

63-3-2

**GENERAL DYNAMICS**

**GENERAL DYNAMICS | CONVAIR**

CATALOGED BY ASTIA  
AS AD NO. 402171

Report No. 8926-150

Material - Aluminum - 2024-T3, 2024-T4, 7178-T6

Effect of Heating Aluminum Alloy Wing Structure  
To 325°F on the Mechanical Properties of its  
Component Materials

P. W. Bergstedt, H. C. Turner, W. M. Sutherland

7 July 1959

ASTIA  
APR 25 1969

Published and Distributed  
under  
Contract AF33(657)-8926

Post Office Box 1950, San Diego 12, California 92161  
Material Post Office Box 2071 273-8000 | Accounting Post Office Box 510

**Best  
Available  
Copy**

Report No. 8926-150

Material - Aluminum - 2024-T3, 2024-T4, 7178-T6

Effect of Heating Aluminum Alloy Wing Structure  
To 325°F on the Mechanical Properties of its  
Component Materials

Abstract:

The Convaair Model 22 subsonic jet transport airplane wing is subjected to a heating cycle which consists of heating from room temperature to 325°F. in 3 hours, holding at 325°F for one hour and cooling to room temperature from 325°F in 4 hours. Such a heating cycle is representative of the heating encountered in an initial Mach. 2 plus supersonic flight. This heating, representing an initial cycle caused (1) a reduction of 15.3 per cent of yield strength in clad 2024-T3 aluminum alloy sheet; (2) a 5.4 per cent reduction in the yield strength of 2024-T4 extrusion; (3) up to 6 per cent reduction in the yield strength of clad 7178-T6 sheet; and a 4.1 reduction in the yield strength of 7178-T6 extrusion. The ultimate strength and elongation of the 2024 alloys were slightly affected by the heating; but the ultimate strengths and elongations of the 7178 alloys underwent changes indicative of slight overaging.

Reference: Bergstedt, P. W., Turner, H. C., Sutherland, W. M.,  
"Scotchweld - Cure Temperature Effects on the Mechanical  
Properties of Aluminum Alloys," General Dynamics/Convaair  
Report MP 59-097, San Diego, California, 7 July 1959.  
(Reference attached).

ACCESS NO.

Title: MATERIAL - ALUMINUM - 7075-T6. EFFECT OF STRETCH STRAIGHTENING ON MECHANICAL PROPERTIES.

Authors: Bergstedt, P. W., Turner, H. C., Sutherland, W. M.

Report No.: 8926-152

Date: 16 November 1959.

Contract: R.E.A. 8010


Contractor: General Dynamics/Convair.

ABSTRACT: Stretching 1" x 1-1/4" x 60" extruded 7075 aluminum alloy bars in the as quenched condition 0.76, 1.74, 1.94, and 2.65 per cent reduced the distortion resulting from machining 82, 78, 86 and 82 per cent, respectively, in comparison with the distortion resulting from machining an "un-stretched" bar. The mechanical properties resulting from stretching and then aging to produce the 7075-T651 condition were:

Treatment*	F <sub>ty</sub> ksi	F <sub>tu</sub> ksi	Elong. % in 2"	F <sub>cy</sub> ksi
No stretch	87.1	95.8	11.0	89.7
0.73% stretch	82.9	90.3	11.0	83.8
1.74% stretch	82.5	90.4	10.7	82.8
1.94% stretch	79.8	87.5	11.0	80.2
2.65% stretch	79.8	87.4	10.5	82.4

\* 370°F., 95 minutes, water quench, stretch, 250°F., 24 hours.

6 pages, 2 tables, 1 figure

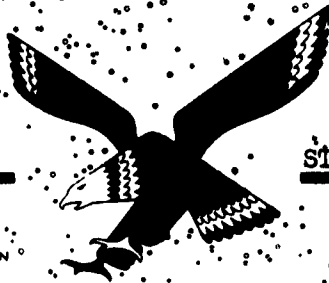

STRUCTURES & MATERIALS LABORATORIES

**CONVAIR**

A DIVISION OF GENERAL DYNAMICS CORPORATION

SAN DIEGO

REPORT MP-59-097

DATE 7. July 1959

MODEL 22

**TITLE**

REPORT NO. MP-59-097

SCOTCHWELD-CURE TEMPERATURE  
EFFECTS ON THE MECHANICAL  
PROPERTIES OF ALUMINUM ALLOYS

MODEL 22

PREPARED BY P. W. Bergstedt  
P. W. Bergstedt

GROUP Materials & Processes Lab.

CHECKED BY: H. C. Turner  
H. C. Turner

REFERENCE Test Request MP-58-401

CHECKED BY W. M. Sutherland  
W. M. Sutherland  
Group Engineer

APPROVED BY E. F. Strong  
E. F. Strong  
Chief of Structures & Materials Labs.

NO. OF PAGES 9

NO. OF DIAGRAMS 6

**REVISIONS**

NO.	DATE	BY	CHANGE	PAGES AFFECTED

ANALYSIS  
PREPARED BY P.W. Bergstedt  
CHECKED BY W.M. Sutherland  
REVISED BY

**CONVAIR**  
A DIVISION OF GENERAL DYNAMICS CORPORATION  
SAN DIEGO

PAGE 1  
REPORT NO. MP-59-097  
MODEL 22  
DATE 7-7-59

Report No. MP-59-097  
Scotchweld-Cure Temperature  
Effects on the Mechanical  
Properties of Aluminum Alloys

INTRODUCTION

Considerable data have been accumulated concerning the effect of heat-exposure treatments upon the mechanical properties of structural aluminum alloys. During the course of the previous work, heat-exposures were chosen which were certain to equal or surpass the severity of the Scotchweld-cure treatment. The work described in this report consisted of a study of the effect of the actual Scotchweld-cure treatment upon the mechanical properties of a few selected aluminum alloy materials.

OBJECT

To determine the effect of the Scotchweld-cure treatment upon the room temperature tensile properties of:

Clad 2024-T3 sheet and plate; 2024-T4 extrusions;  
Clad 7178-T6 sheet and plate; 7178-T6 extrusions.

CONCLUSIONS

The Scotchweld exposure treatment caused definite changes in the tensile properties of the test materials. The high points of these variations are listed below.

1. By causing partial relief of cold work, the Scotchweld exposure lowered the yield strength of the clad 2024-T3 materials by as much as 15.3 per cent. However, ultimate tensile strength and elongation of this material was only slightly affected.
2. Maximum yield strength reduction of the 2024-T4 extruded material was 5.4 per cent. Ultimate strength of this material was least affected of all the test materials, and elongation was increased for all gauges.
3. The tendency of the 7178-T6 materials to over-age caused yield strength reductions of up to 6 per cent in the clad stock and 4.6 per cent in the extrusions. These materials exhibited the highest losses in ultimate strength, up to 4.1 per cent for both forms. Elongation reductions were also clearly observed in these materials, but the losses did not appear excessive for this particular type of property.

TEST MATERIALS

Four materials were subjected to test:  
Clad 2024-T3 sheet and plate  
2024-T4 extrusions  
Clad 7178-T6 sheet and plate  
7178-T6 extrusions.

## ANALYSIS

PREPARED BY P. W. Bergstedt  
CHECKED BY W. M. Sutherland  
REVISED BY

## CONVAIR

A DIVISION OF GENERAL DYNAMICS CORPORATION  
SAN DIEGO

PAGE 2

REPORT NO. MP-59-097  
MODEL 22  
DATE 7-7-59

TEST MATERIALS (Continued)

Seven gauges, 0.080, 0.100, 0.125, 0.150, 0.190, 0.250, and 0.312, were sampled of each material. (Two gauges, 0.100 and 0.250, of the clad 7178-T6 material were not available.)

TEST SPECIMEN

A standard flat tensile specimen was used throughout the test. This type of sample has a 0.75" shoulder suitable for jaw-grips and a 0.5"x2.25" reduced test-section. The specimens were prepared in accordance with Federal Test Method Standard 151.

PROCEDURE

The work described herein was confined to tension testing, and a longitudinal sampling plan was employed for all of the materials. Six samples were required from each material -- three controls and three samples for exposure to the Scotch-weld-cure cycle.

The 1"x9" coupons were cut side-by-side from the sheet and plate stock and end-to-end from pre-selected legs of the extrusions. The coupons were numbered consecutively in every instance. Odd-numbered samples were used for control tests, and even-numbered specimens were exposed to the Scotch-weld-cure treatment.

Small holes were drilled in one shoulder of each of the latter specimens, and, using suitable spacers, the samples were strung on aluminum wire. The specimens (in a fully-machined condition) were then suspended within a Model 880 wing being readied for the Scotch-weld cure.


Two exposure-runs were performed. The first was for the clad 2024-T3 sheet and plate. (Ref: Test Request MP-58-401) The second run accomplished the exposure of the other three test materials. During the first run two thermocouples were used; one was attached to one of the 0.080" samples, and the second measured the temperature of one of the 0.312" specimens. Since variations between the temperature-records from the two thermocouples were very slight, only one thermocouple was used during the second run. The two time-temperature records were copied for inclusion in this report (see Fig. 1).

The tensile tests were performed in a 60,000 lb. Tinius Olsen Universal Testing Machine. Standard practice was followed for all testing.

RESULTS AND DISCUSSION

The tensile test data are recorded in Tables I through IV. The changes in tensile properties attributable to the Scotch-weld-cure exposure are also shown in the tables. To provide a means for rapid appraisal of the Scotch-weld-cure effects, the average tensile property changes were converted to percentages (based upon as-received results) and re-tabulated in Table V.

FIG. 1. TEMPERATURE VS. TIME — SCOTCHWELD CURE TREATMENT —  
TENSILE SPECIMENS EXPOSED TO ACTUAL CYCLE WITH WING

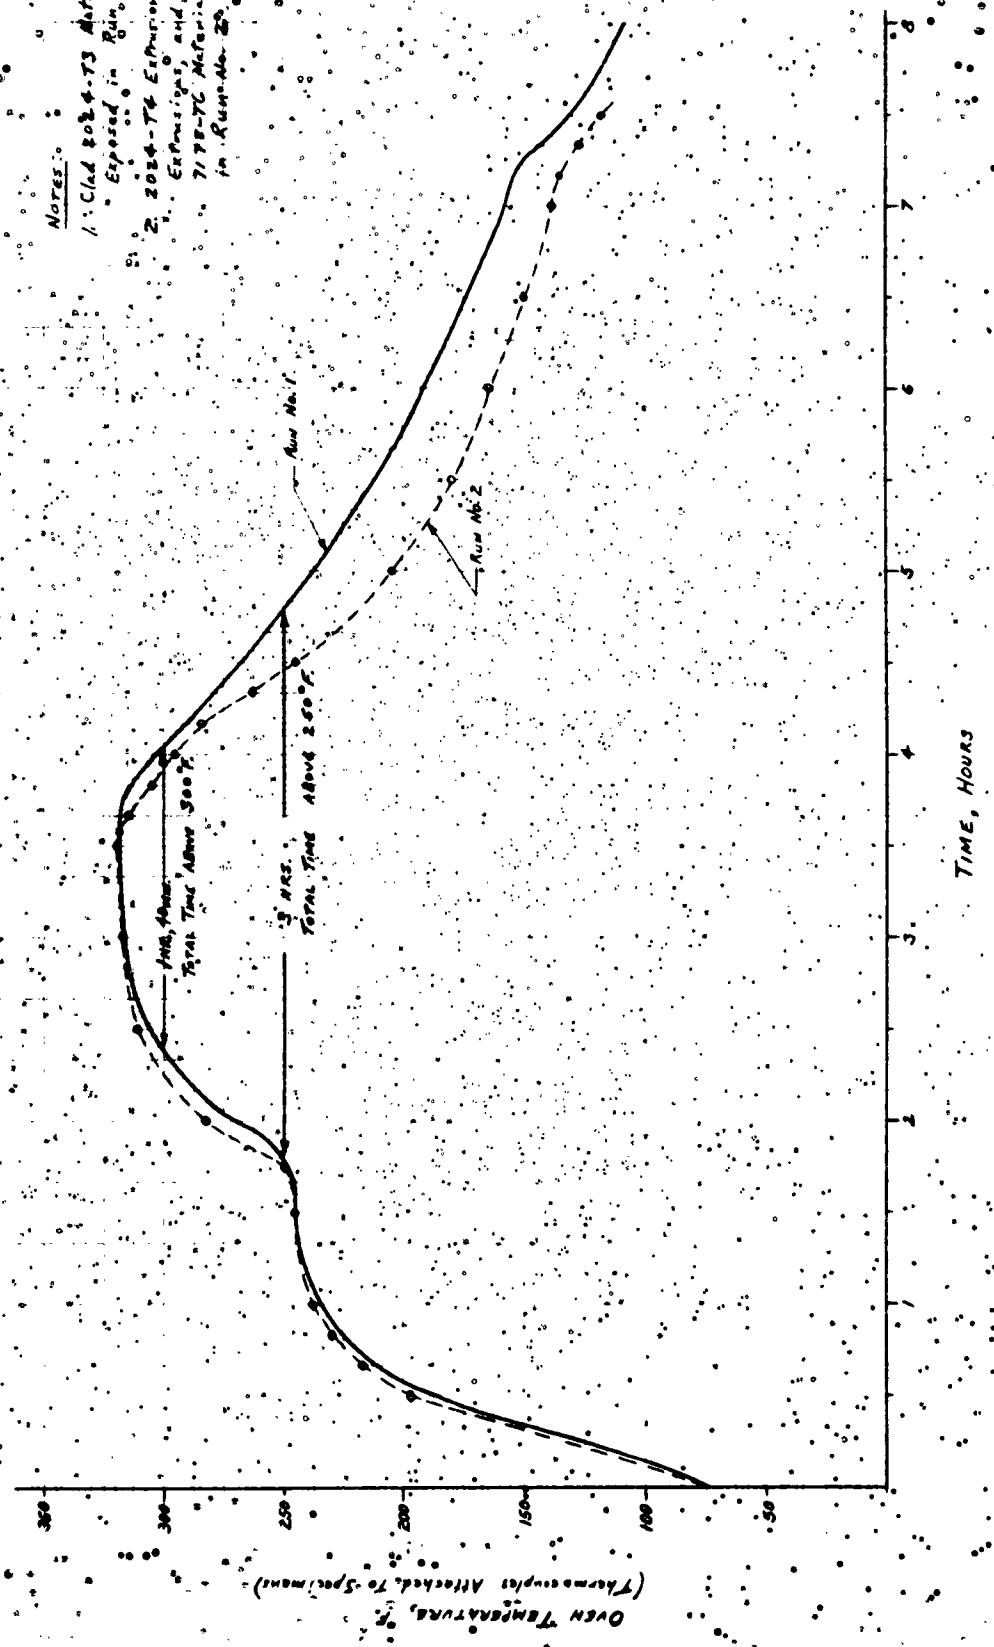

Notes:

1. Clad 2024-T3 Materials Exposed in Run No. 1.
2. 2024-T6 Exports, 7178-T6 Exports, and Clad 7178-T6 Materials Exposed in Run No. 2.

OVEN TEMPERATURE, °F  
(Thermocouples Attached to Specimens)

TIME, HOURS



TABLE I. EFFECT OF SCOTCHWELDING UPON THE TENSILE PROPERTIES OF C140 1178-T6 SHEET AND PLATE

FORM 17

TEST MATERIAL	AS RECD PROPERTIES			POST-SCOTCHWELD PROPERTIES			APPROXIMATE CHANGE IN PROPERTIES DUE TO SCOTCHWELDING		
	YIELD STRENGTH F <sub>y</sub> , KSI (0.2% OFFSET)	TENSILE STRENGTH F <sub>t</sub> , KSI 2" GAGE	ELONGATION %, 2" GAGE	YIELD STRENGTH F <sub>y</sub> , KSI (0.2% OFFSET)	TENSILE STRENGTH F <sub>t</sub> , KSI 2" GAGE	ELONGATION %, 2" GAGE	YIELD STRENGTH F <sub>y</sub> , KSI (BASED UPON AVERAGE RESULTS)	TENSILE STRENGTH F <sub>t</sub> , KSI (BASED UPON AVERAGE RESULTS)	ELONGATION %, 2" GAGE
C140 1178-T6 SHEET	75.0	83.1	14.0	73.2	79.2	10.5			
	74.0	82.8	12.0	73.7	79.3	11.0			
	75.5	81.7	11.0	73.7	78.3	11.0			
	AVG: 75.0	82.0	12.3	AVG: 73.5	79.3	10.8	-2.3	-2.7	-1.5
C140 1178-T6 PLATE	78.8	85.0	12.0	75.6	81.8	10.5			
	77.9	84.3	13.0	74.9	81.5	10.5			
	78.2	83.1	12.0	75.1	81.5	10.7			
	AVG: 78.3	84.4	12.5	AVG: 75.1	81.5	10.7	-3.2	-3.9	-1.6
C140 1178-T6 PLATE	81.9	86.6	12.0	76.1	82.9	12.0			
	80.5	85.6	11.0	76.4	82.6	12.0			
	80.9	86.0	11.0	76.2	82.4	10.5			
	AVG: 80.9	86.1	11.3	AVG: 76.2	82.6	11.5	-4.9	-3.5	-1.3
C140 1178-T6 PLATE	71.9	84.9	12.0	75.1	81.2	10.0			
	71.3	84.8	12.0	75.8	81.7	12.0			
	71.6	84.7	12.0	75.4	81.4	12.5			
	AVG: 71.6	84.6	12.3	AVG: 75.4	81.4	11.5	-4.2	-3.2	-0.8
C140 1178-T6 PLATE	79.5	84.1	14.0	75.0	80.8	11.5			
	78.7	83.1	13.0	74.2	79.9	12.0			
	71.7	82.3	13.0	75.3	81.0	12.0			
	AVG: 78.6	83.2	13.3	AVG: 74.8	80.6	11.8	-3.8	-2.6	-1.5

TABLE II: EFFECT OF SCOTCHWELDING UPON THE TENSILE PROPERTIES OF 2024-T3 ALUMINUM

ALLOY & CONDITION	TENSILE STRENGTH (MPa)	TENSILE ELONGATION (%)	TENSILE REDUCTION OF AREA (%)	AS RECD. PROPERTIES		POST-SCOTCHWELDED		APPARENT CHANGE IN PROPERTIES DUE TO SCOTCHWELDING	
				TENSILE STRENGTH (MPa)	TENSILE ELONGATION (%)	TENSILE STRENGTH (MPa)	TENSILE ELONGATION (%)	YIELD STRENGTH (MPa)	ELONGATION (%)
0.080"	51.9	64.7	14.0	49.7	64.4	19.0			
	52.7	65.0	16.5	49.5	64.1	20.0			
	52.8	64.1	16.0	49.1	64.2	19.0			
	AVG: 52.2	64.6	15.5	AVG: 49.4	64.2	19.0		-2.8	-0.4
0.100"	52.6	65.6	18.0	50.5	65.2	18.0			
	52.5	64.1	18.5	50.4	64.5	18.0			
	52.7	64.3	17.5	50.6	64.7	19.5			
	AVG: 52.6	64.0	18.0	AVG: 50.5	64.8	18.8		-2.1	+0.8
0.125"	48.5	62.7	20.0	45.7	61.4	21.0			
	48.1	62.4	18.0	46.2	62.1	22.0			
	47.5	62.1	19.5	45.9	61.3	20.0			
	AVG: 48.0	62.4	19.2	AVG: 45.9	61.6	21.0		-2.1	+0.8
0.150"	48.1	62.0	18.0	45.8	61.1	22.5			
	48.3	63.0	20.5	46.0	62.8	20.0			
	48.6	62.5	20.0	46.5	61.9	22.0			
	AVG: 48.3	62.2	19.5	AVG: 46.1	61.3	21.5		-2.2	+0.9
0.1908"	53.0	67.4	17.0	50.7	66.6	16.5			
	53.1	67.1	17.5	51.2	64.3	17.5			
	53.9	67.4	17.0	51.7	65.1	16.5			
	AVG: 53.1	67.2	17.2	AVG: 51.0	66.3	17.5		-2.1	+0.9
0.250"	56.4	73.5	14.5	54.7	72.7	18.5			
	56.8	73.3	15.0	54.7	73.1	19.5			
	57.0	74.4	14.0	54.6	73.1	16.5			
	AVG: 56.7	72.7	14.5	AVG: 54.7	73.0	16.8		2.0	-0.7
0.312"	57.5	75.1	15.5	56.1	74.5	16.5			
	57.5	75.1	15.0	56.0	74.8	17.0			
	57.9	75.5	15.0	55.4	74.1	16.0			
	AVG: 57.6	75.2	15.2	AVG: 55.8	74.5	16.5		1.8	+0.7

TABLE 1. EFFECT OF SCOTCHBULDING ON THE TENSILE PROPERTIES OF 7175-T6 ALUMINUM

FORM 75  
CONWAY  
SANT BIEGO

ALLOY & NOMINAL CONDITION THICKNESS	AS REC'D PROPERTIES		POST-SCOTCHBULDING PROPERTIES		APPROXIMATE CHANGE IN PROPERTIES DUE TO SCOTCHBULDING	
	YIELD STRENGTH (KSI)	TENSILE STRENGTH (KSI)	YIELD STRENGTH (KSI)	TENSILE STRENGTH (KSI)	YIELD STRENGTH (KSI)	TENSILE STRENGTH (KSI)
0.080"	85.0	91.8	82.2	88.9	-2.8	+7.1
	84.8	91.7	79.5	87.2	-5.3	+5.5
	83.6	90.7	82.3	89.1	-1.3	+8.4
	AVG: 84.5	91.4	AVG: 81.3	88.3	-3.2	+6.8
0.100"	88.3	95.5	86.6	93.1	-1.7	+4.6
	87.8	95.0	87.6	94.0	-0.2	+9.0
	89.3	96.2	87.0	93.1	-2.3	+3.9
	AVG: 88.5	95.6	AVG: 87.1	93.4	-1.4	+7.8
0.125"	91.5	97.3	86.6	93.3	-4.9	+1.7
	90.7	97.3	86.3	93.3	-4.4	+2.6
	91.5	97.6	87.4	93.6	-4.1	+2.1
	AVG: 91.2	97.4	AVG: 86.8	93.4	-4.4	+2.2
0.150"	90.6	96.9	87.8	94.0	-2.8	+7.4
	89.6	96.5	85.8	93.4	-3.8	+3.8
	89.2	95.1	86.0	92.9	-3.2	+3.7
	AVG: 89.5	96.2	AVG: 86.5	93.4	-3.0	+3.9
0.180"	95.6	104.8	90.7	97.5	-4.9	+6.8
	95.3	101.0	92.6	95.2	-2.7	+4.9
	96.7	103.5	93.4	98.4	-3.3	+17.7
	AVG: 95.9	102.8	AVG: 92.2	98.0	-3.7	+10.1
0.250"	88.7	94.8	84.3	91.2	-4.4	+6.5
	70.2	95.9	84.8	92.5	14.6	-6.3
	90.7	95.8	84.6	92.5	-6.1	+6.8
	AVG: 81.7	95.5	AVG: 85.7	92.1	-4.0	+6.4
0.312"	86.4	94.0	86.8	94.2	0.4	+0.2
	88.5	95.0	86.1	93.4	-2.4	+8.4
	87.4	94.8	82.0	91.4	-5.4	+6.6
	AVG: 87.5	94.9	AVG: 85.0	93.0	-2.5	+5.5

TABLE IV. EFFECT OF SCOTCHBELDING UPON THE PROPERTIES OF GLAD 2024 STEEL AND PLATE

TEST MATERIAL	AS REC'D PROPERTIES		POST-SCOTCHBELD PROPERTIES		PERCENT CHANGE IN PROPERTIES PER 10 MIL THICKENING BASED UPON AVERAGE RESULTS	
	F <sub>U</sub> KSI (TENSILE)	E <sub>L</sub> KSI (2% GAGE)	F <sub>U</sub> KSI (TENSILE)	E <sub>L</sub> KSI (2% GAGE)	YIELD POINT	YIELD POINT
ALLOY 6 NOMINAL THICKNESS	51.9	70.0	47.9	67.5		
	51.9	69.9	47.6	67.4		
	51.9	70.0	48.0	67.3		
	AVG: 51.9	70.0	AVG: 47.8	67.4	-4.1	-2.6
CLAD 0.080"	52.3	69.1	48.9	68.3		
	52.3	69.0	48.7	68.4		
	51.6	69.0	48.9	67.7		
	AVG: 52.1	69.0	AVG: 48.8	68.1	-3.3	-0.9
0.100"	49.1	67.7	47.0	67.1		
	49.2	67.7	45.9	66.9		
	49.2	67.5	46.2	67.1		
	AVG: 49.2	67.6	AVG: 46.4	67.0	-2.8	-0.6
0.160"	52.6	68.7	50.0	67.1		
	52.6	68.7	48.7	67.0		
	52.8	68.5	49.3	66.7		
	AVG: 52.7	68.6	AVG: 49.3	66.9	-3.4	-1.7
CLAD 0.170"	50.6	70.3	45.1	68.0		
	49.2	70.0	45.8	68.0		
	49.3	70.1	43.8	67.5		
	AVG: 49.7	70.1	AVG: 44.9	67.8	-4.8	-2.3
CLAD 0.250"	52.2	65.0	47.2	63.2		
	52.0	65.0	48.2	63.0		
	52.5	65.4	47.1	62.2		
	AVG: 52.2	65.1	AVG: 47.5	63.1	-4.7	-2.0
0.312"	64.0	69.4	54.2	66.4		
	63.7	69.2	54.2	66.2		
	63.9	69.4	53.9	66.1		
	AVG: 63.9	69.3	AVG: 54.1	66.2	-9.5	-4.1

TABLE V. APPARENT EFFECT OF SCOTCHWELD-EXPOSURE UPON THE TENSILE PROPERTIES OF FOUR ALUMINUM-ALLOY MATERIALS.

MECHANICAL PROPERTY UNDER CONSIDERATION	MATERIAL DESCRIPTION <sup>1</sup> ALLOY, CONDITION, AND FORM	PERCENT CHANGE IN TENSILE PROPERTY AFTER SCOTCHWELD-EXPOSURE							AVG.
		NOMINAL THICKNESS OF MATERIAL, IN.							
		0.080	0.100	0.125	0.150	0.170	0.250	0.312	
Tensile Yield Strength	CLAD 2024-T3 SHEET & PLATE	-7.9	-6.3	-5.7	-6.5	-9.7	-9.0	-15.3	-8.6
	CLAD 7178-T6 SHEET & PLATE	3.0	—	4.1	6.0	5.3	—	4.8	4.6
	2024-T4 EXTRUSION	5.4	4.0	4.4	4.6	4.0	3.5	3.1	4.1
	7178-T6 EXTRUSION	3.8	1.6	4.8	3.4	3.9	4.5	2.9	3.6
Ultimate Tensile Strength	CLAD 7178-T6 SHEET & PLATE	3.3	—	3.4	4.1	3.8	—	3.1	3.5
	7178-T6 EXTRUSION	3.4	2.3	4.1	2.9	3.7	3.6	2.0	3.1
	CLAD 2024-T3 SHEET & PLATE	3.7	1.3	0.9	2.5	3.3	3.1	1.6	2.3
	2024-T4 EXTRUSION	0.6	1.8	1.3	1.4	4.3	0.9	0.9	1.2
Elongation	CLAD 7178-T6 SHEET & PLATE	12.2	—	13.0	1.8	6.5	—	11.3	8.2
	7178-T6 EXTRUSION	7.8	2.8	7.4	2.0	9.4	8.9	4.5	4.3
	CLAD 2024-T3 SHEET & PLATE	2.3	2.5	7.1	0.5	0	3.0	0	1.2
	2024-T4 EXTRUSION	22.6	4.4	9.4	10.3	1.7	15.9	8.6	10.4

<sup>1</sup> For each tensile property, the materials are listed in order of decreasing deleterious effects.

<sup>2</sup> These percentages were calculated from the average values shown in Tables I - II.