

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.					
1. REPORT DATE (DD-MM-YYYY) 30-06-2017		2. REPORT TYPE Performance/Technical Report (Quarterly)		3. DATES COVERED (From - To) 04/01/2017 – 06/30/2017	
4. TITLE AND SUBTITLE A Hybrid Approach to Composite Damage and Failure Analysis Combining Synergistic Damage Mechanics and Peridynamics				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER N00014-16-1-2173	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Dr. Ramesh Talreja				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Texas A&M Engineering Experiment Station (TEES) 400 Harvey Mitchell Parkway, Suite 300 College Station, Texas 77845				8. PERFORMING ORGANIZATION REPORT NUMBER M1601473 / 505170-00001/2	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 875 N. Randolph Street, Suite 1425 Arlington, VA 22203-1995				10. SPONSOR/MONITOR'S ACRONYM(S) ONR	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION / AVAILABILITY STATEMENT unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT <i>The work performed in the reporting period has been focused on completion of Task 1.1, and continuation of Task 1.2 and Task 2.2 described in the project proposal. The activities related to Task 1.1 are formation of cracks in a computational micromechanics failure analysis of a representative volume element containing disordered fiber distributions and Task 1.2 concerns growth and instability of initiated cracks in the environment of the disordered fiber distributions. The activities related to Task 2 cover modeling of interface bonds between different phases in a composite.</i>					
15. SUBJECT TERMS Computational micromechanics; Cavitation induced cracking; Peridynamics; Porous media					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT	b. ABSTRACT	c. THIS PAGE			William Nickerson
U	U	U	SAR	6	19b. TELEPHONE NUMBER (include area code) 703-696-8485

Quarterly Progress Report, April 1 – June 30, 2017

A Hybrid Approach to Composite Damage and Failure Analysis Combining Synergistic Damage Mechanics and Peridynamics

Award Number N00014-16-1-2173

DOD – NAVY – Office of Naval Research

PI: Ramesh Talreja

Co-PI: Florin Bobaru

Executive Summary

The work performed in the reporting period has been focused on completion of Task 1.1, and continuation of Task 1.2 and Task 2.2 described in the project proposal. The activities related to Task 1.1 are formation of cracks in a computational micromechanics failure analysis of a representative volume element containing disordered fiber distributions and Task 1.2 concerns growth and instability of initiated cracks in the environment of the disordered fiber distributions. The activities related to Task 2 cover modeling of interface bonds between different phases in a composite.

Task 1.2 Ply level constrained cracking

Task 1.1 dealt with initiation of micro-level cracking. It has been essentially completed and most results were reported in previous quarterly reports. Figure 1 illustrates the process of crack initiation from clustering of cavitation points in the matrix. On the left is the representative volume element (RVE) consisting of nonuniformly distributed fibers embedded as a circular cell within the homogenized composite of outer rectangular boundary. The assembly is subjected to a uniform displacement normal to the fiber axis. From the stress and strain fields calculated by a finite element model (left in Fig. 1), and application of a criterion for cavitation in the matrix, the first and subsequent points of dilatation induced cavitation are found. Two stages of the evolution of cavitation are shown in Fig. 1. In the early stage (middle figure), diffuse points of cavitation occur, while clustering of the cavitation occurs as the applied transverse tension increases.

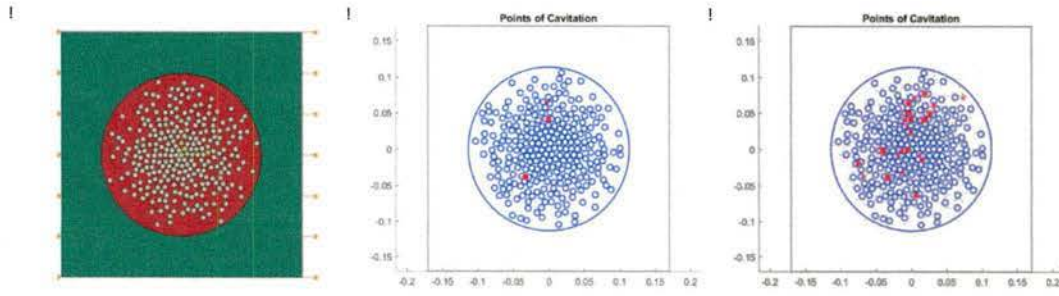


Figure 1. The RVE consisting of discrete disordered fiber distribution is embedded as a circular cell within a homogenized composite region (left) and the assembly is subjected to uniform tension. The figure in the middle shows early stage of cavitation and the one to the right shows a later stage. Red dots indicate the points where cavitation occurs under transverse tension.

Multiple realizations of RVEs are generated and for each realization representing a certain degree of fiber mobility during the manufacturing process, the formation of the first crack is studied. The criterion for crack formation is occurrence of ~ 4 cavitations along a strip oriented approximately normal to the loading direction. Each cavitation is assumed to cause fiber/matrix debonding, as described in previous reports. Coalescence of the adjacent disbands results in initiation of a transverse crack. Figure 2 (a) plots the applied strain at which first cavitation occurs and when the first crack forms. The results are plotted against increasing mobility of fibers given by the radial deviation from initial positions in the dry bundle state.

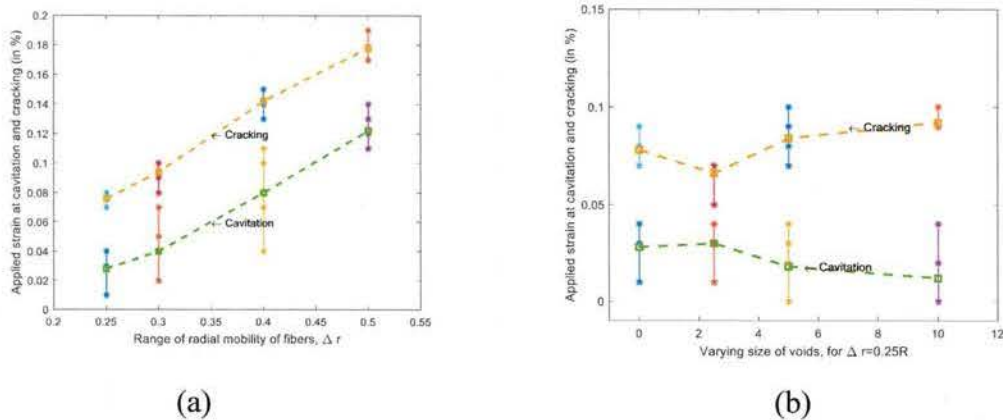


Figure 2. (a): The applied strain at which transverse cracking occurs and at which the first cavitation causing fiber/matrix debonding occurs versus the radial mobility of fibers during the resin infusion process (for a fixed angular mobility). (b): The same strains as in (a) when voids of different size are present at one fiber mobility.

The failure analysis described above is conducted with micro-voids present between the fibers. The results for one case of fiber mobility (i.e., one case of fiber clustering) are plotted in Fig. 2(b). The results suggest that generally, the strain to crack formation is higher by approximately the same amount at all void sizes. These strains increase with fiber mobility, i.e. with reduced fiber clusters. However, when micro-voids are present, the effect is to cause cavitation as well as crack formation earlier.

The ongoing research will focus on continued growth of the initiated transverse cracks. Conditions for instability of crack growth will be examined.

Task 2. Peridynamic modeling of failure at the interface between composite phases

Background

Lead-free solder joints used in microelectronics and electronic packaging for critical mission defense applications tend to fail because of the presence of intermetallic compounds in the solder matrix material. In Figure 3 (a) we show an example of a failed solder joint from repeated drop-tests. The fractures tend to happen along the intermetallic component or at the interface between the two components of the composite. The availability of microscale experimental data in these systems make them a good choice for testing the peridynamic modeling of failure in composites.

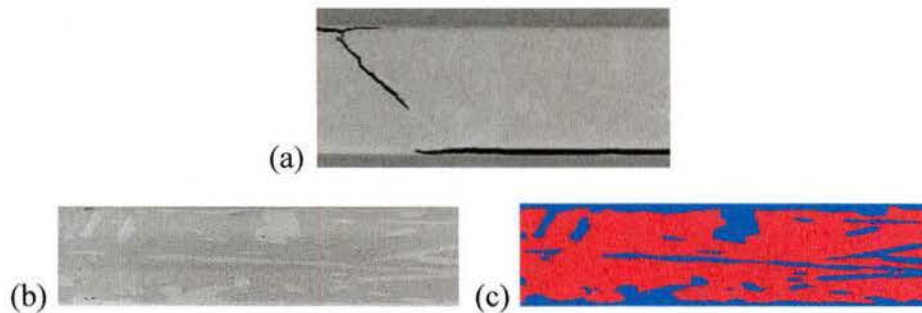


Figure 3. (a) Microscale SEM image of a failed solder joint; (b) selection of a sample microstructure to be used for modeling; (c) the digitized material map for the microstructure in (b).

Approach and Results

To this end, we create a digitized model of the two-phase composite (see Figure 3b and 3c), in which the blue phase is the brittle phase. The properties of the bonds between peridynamic nodes in the matrix (SAC305) and the inclusions (AuSn4) are calibrated to their respective composition, while for the bonds that cross material interfaces between these two components, we use interface bonds (see Figure 4). The properties of these bonds are based on a “mixture” of the properties of the individual phases.

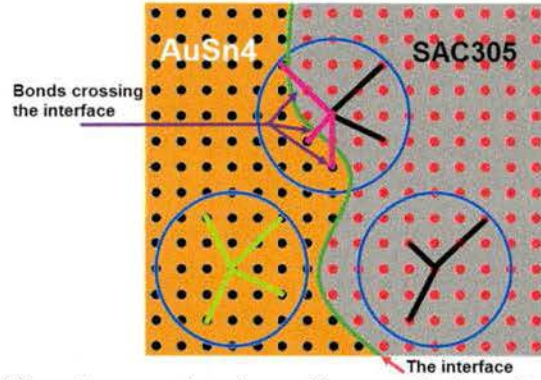


Figure 4. Assignment of bond properties depending on the location of its end-nodes. Interface bonds have special properties.

Using boundary data from time-series of component-level finite element simulations, the peridynamic results show growth of cracks that propagate mostly along the material interfaces between the inclusions and the matrix (see Figures 5a and 5b).

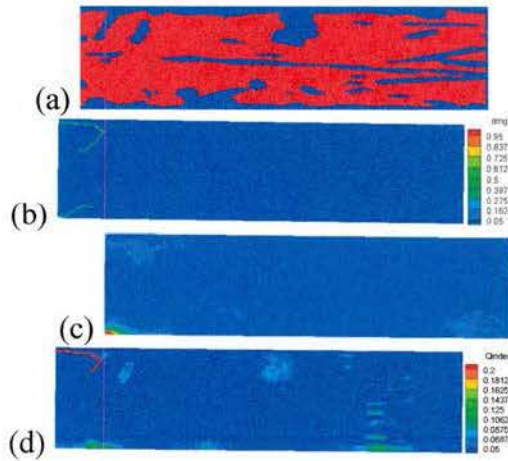


Figure 5. (a) the digitized composite sample; (b) damage index map showing the presence of two main crack lines obtained with the PD model; (c) map of strain energy density; (d) the new quasi-index damage is a predictor of failure.

As in the case of FRCs, one wants to primarily increase reliability of electronic components and avoid failure. The strain energy density, in a homogeneous material, is a good measure for estimating the propensity of failure at a point. However, for composite materials, the strain energy density is no longer a good indicator of where failure might occur (see Figure 5c). This is why we introduced a new measure, a precursor of fracture, which can give an indication of which points are most likely to fail, before actual failure happens. The “quasi-damage index”, shown in the formula below, is a point-wise measure that uses the strain in a bond between nodes i and j , the total number of bonds at the node x_i , $N(x_i)$, and $s_0(i, j)$, the critical strain for bond (i, j) .

$$Q(x_i) = \frac{1}{N(x_i)} \sum_{j=1}^{N(x_i)} \min\left(\frac{s(i,j)}{s_0(i,j)}, 1\right)$$

With the quasi-damage index, we are able to foresee where the cracks may initiate from. The comparison between Figures 5b and 5d prove this point.

The ongoing research will extend this approach to investigate failure in fiber-reinforced composites. The draft for a journal paper on the topic shown above is in preparation.