

## BRIEF COMMUNICATION OPEN

## Unavoidable disorder and entropy in multi-component systems

Cormac Toher<sup>1</sup>, Corey Oses<sup>1</sup>, David Hicks<sup>1</sup> and Stefano Curtarolo<sup>1</sup>

The need for improved functionalities is driving the search for more complicated multi-component materials. Despite the factorially increasing composition space, ordered compounds with four or more species are rare. Here, we unveil the competition between the gain in enthalpy and entropy with increasing number of species by statistical analysis of the AFLOW data repositories. A threshold in the number of species is found where entropy gain exceeds enthalpy gain. Beyond that, enthalpy can be neglected, and disorder—complete or partial—is unavoidable.

npj Computational Materials (2019)5:69; <https://doi.org/10.1038/s41524-019-0206-z>

## INTRODUCTION

The formation of materials in the tangible world, enjoying easy-life at room temperature and pressure, is governed by the Gibbs free energy. Enthalpy usually makes up a large part of it, and, for the last 2 decades, the search for new materials has mostly focused on enthalpy optimization. A plethora of methods were proposed: e.g., cluster expansion,<sup>1</sup> genetic-<sup>2</sup> and combinatorial algorithms.<sup>3</sup> In trying to cure the Maddox curse<sup>4</sup> (Maddox: “One of the continuing scandals in the physical sciences is that it remains in general impossible to predict the structure of even the simplest crystalline solids from a knowledge of their chemical composition”), these approaches were all somewhat successful in predicting and discovering systems made up of few species. At least this was the impression: polymorphs were still able to escape from the enthalpic jail! While the need for functionalities was driving the search for more complicated materials, something unexpected happened: the discovery of high-entropy alloys.<sup>5,6</sup> The ideal scenario of phase transitions—in which precursors constantly seek the most stable configuration—was shattered by the acceptance that disorder is useful. Skeptics considered high-entropy alloys only a remake of solid-solutions. In the meantime, new families appeared: entropy-stabilized oxides, high-entropy carbides and borides. Each carrying a panoply of unexpected properties.

## RESULTS AND DISCUSSION

Are entropic materials the exception?

The question requires the disentanglement of the “enthalpy versus entropy” dichotomy. Big-data statistical analysis gives the answer. Let us consider the AFLOW.org ab-initio materials repository<sup>7</sup> and analyze its compounds’ energies with the associated tools.<sup>8,9</sup> The recursive formation enthalpy “gain” of an  $N$ -species ordered compound (called  $N$ -compound) with respect to combinations of  $\{1, \dots, N-1\}$ -species ordered sub-components,  $\Delta H[N]\{1, \dots, N-1\}$ , is defined as the energetic distance of the enthalpy of the  $N$ -compound,  $H[N]$ , below the  $\{1, \dots, N-1\}$  convex-hull hyper-surface  $H_{\text{hull}}\{1, \dots, N-1\}$  generated from its  $\{1, \dots, N-1\}$ -species components:  $\Delta H[N]\{1, \dots, N-1\} \equiv H_{\text{hull}}\{1, \dots, N-1\} - H[N]$  if  $H[N] < H_{\text{hull}}\{1, \dots, N-1\}$  (for binary compounds,  $\Delta H[2][1]$  is equivalent to the usual formation enthalpy; for  $N > 2$ , the formation

enthalpies can be written as sums of the recursive gains) and zero otherwise ( $\Delta H[N]\{1, \dots, N-1\}$  is conceptually similar to the stability criterion  $\delta_{\text{sc}}$  described in ref. <sup>9</sup>, except with all  $N$ -species entries removed from the pseudo-hull). Physically,  $\Delta H[N]\{1, \dots, N-1\}$  represents the enthalpy gain to create an ordered  $N$ -compound out of all the combinations of ordered  $\{1, \dots, N-1\}$ -ones. Gain expectations can be obtained by the analysis of metal alloy phase diagrams “constructible” out of the AFLOW.org data.  $\langle \Delta H \rangle$  is shown in Fig. 1a for  $N = 2, 3, 4$ , and as cohesive energy for  $N = 1$ .

Finding new  $N$ -compounds becomes difficult


While 59% (588) of the binaries show enthalpy gain by forming a total of 1995 2-compounds, only 16% (2237) of ternaries produce 3040 3-compounds and just 426 (0.3%) quaternaries form 4-compounds. Phase separation is overwhelming. Contrary to common belief, the trend indicates that despite the combinatorially-growing number of potential configurations, finding accommodating prototypes becomes harder with increasing  $N$ .

Entropy takes over

The surviving combinations of species forming new compounds become vulnerable with increasing  $N$ . The expectation of  $\Delta H$  is  $\sim 181$  meV/atom for binaries. It drastically reduces to  $\sim 7$  meV/atom for ternaries, practically disappearing ( $< 0.1$  meV/atom) for quaternaries. 434 binary, 192 ternary but only 10 quaternary systems have a large enthalpy gain (defined as exceeding 100 meV/atom): the frequency distributions of enthalpy gains for all systems are displayed in Fig. 1b. The numbers are compared to disorder promotion where the ideal scenario is considered for simplicity.<sup>10</sup> Figure 1a shows the ideal entropic contribution at room temperature for the fully ( $N$ ) and partially disordered ( $N-1$ ,  $N-2$ ,  $N-3$ ) systems. Since the  $N-1$  component systems could also feature disorder, i.e., the  $N$  component system could phase-separate into multiple disordered phases, the  $\log(N) - \log(N-1)$  entropy gain is also plotted (black dashed line). Note that the latter already exceeds the enthalpy gain for  $N = 3$ . The reducing probability of having  $N$ -compounds—also recursively applying to sub-components—compounded with the drastically decreasing

<sup>1</sup>Department of Mechanical Engineering and Materials Science, Duke University, Durham, NC 27708, USA  
Correspondence: Stefano Curtarolo (stefano@duke.edu)

Received: 20 December 2018 Accepted: 6 June 2019  
Published online: 10 July 2019

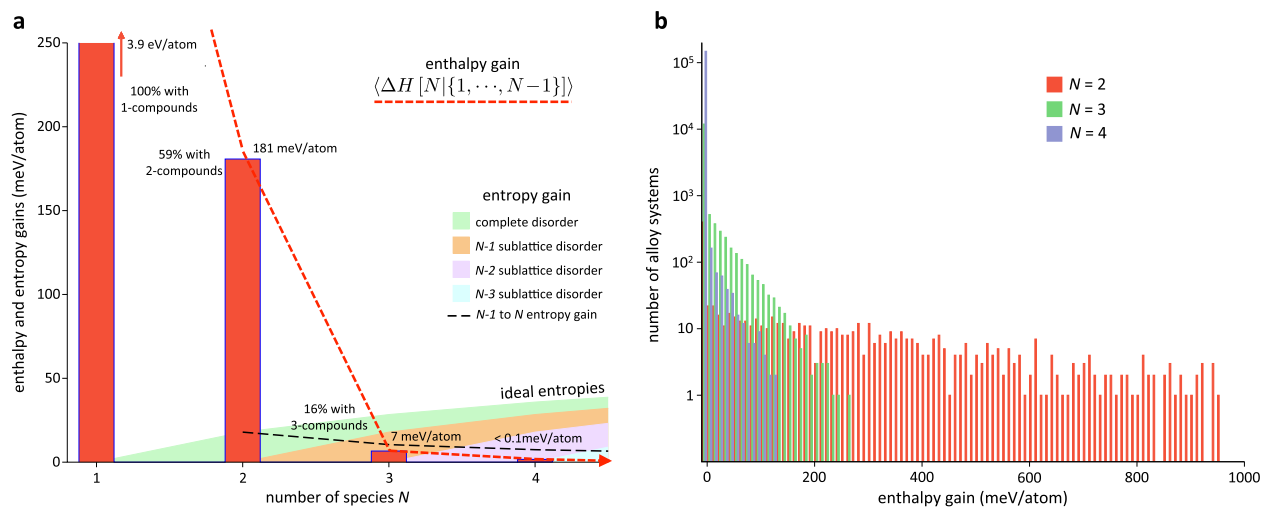

**Fig. 1** Enthalpy and entropy gains. **a** Expectation of enthalpy-gain  $\langle \Delta H [N] \{1, \dots, N-1\} \rangle$  and ideal entropy contributions as functions of number of species,  $N$ . Even at room temperature, entropy eventually overwhelms enthalpy in controlling phase stability of multi-component systems. **b** Enthalpy gain distribution for  $N = 2, 3, 4$ ; gains decrease with increasing number of species

enthalpic gain and the monotonic entropic promotion, indicates that around the threshold  $N \sim 4$ , entropy takes over the stability of the system.

### Beyond metals

The analysis focuses on the extensive AFLOW set of metallic compounds; a similar analysis for non-metals requires formation enthalpy corrections.<sup>11</sup> Mixing different types of bonding can change the entropy threshold by adding additional enthalpic stabilization, leading to a shift of the onset of the entropic promotion ( $N$  increases). It is not a coincidence: entropy stabilized oxides were discovered with five metallic species mixed with oxygen,<sup>12</sup> and high-entropy-carbides and borides were also synthesized with five metallic species plus carbon<sup>13</sup> or boron.<sup>14</sup> There, oxygen, carbon, and boron are “spectator” species. The devil is in the details: reciprocal systems might be able to reduce the number of the mixing species, thanks to the additional entropic stabilization of every equivalent sublattice.

### The future

Ramifications of the analysis are intriguing. Disordered systems can lead to remarkable properties<sup>15–17</sup>—unexpected from the homologous crystalline counterparts—enabling revolutionary technologies. We just need to search for materials with a different mindset. (I) The search for multi-component systems, performed with enthalpy optimization, is futile. With increasing  $N$ , the discovery probability decreases, and, even if an ordered material is found, it would be overwhelmed by engulfing disorder. High-entropy promotion occurs at  $\sim 4$  mixing species ( $\sim 5+$  with different bond types). (II) Sluggish kinetics at low temperatures can be a blessing.<sup>18</sup> Disorder is hard to cure, and high entropy solid-solutions synthesized at high-temperature can survive low-temperature phase separation<sup>13,18</sup> while providing valuable technological applications.<sup>15</sup> (III) Maddox’s scandal was only an apparent curse. It was actually a blessing as it forced statistical analysis of the enthalpy versus entropy interplay. Modeling can no longer ignore disorder—often neglected due to compelling difficulties. Advances in complex multi-component materials research will be driven by embracing disorder. It is unavoidable.

### METHODS

Calculations of the enthalpy gain are performed using the AFLOW-CHULL module, using the command:

```
aflow --chull --alloy = <system> --print = json,
```

where <system> is a list of the elements in the alloy system. The enthalpy gain is contained in the JSON output file under the keyword  $N+1\_energy\_gain$ . To enhance statistical significance, only metallic alloy systems composed of the elements Ag, Al, Au, Ba, Be, Bi, Ca, Cd, Co, Cr, Cu, Fe, Ga, Hf, Hg, In, Ir, K, La, Li, Mg, Mn, Mo, Na, Nb, Ni, Os, Pb, Pd, Pt, Re, Rh, Ru, Sc, Sn, Sr, Ta, Tc, Ti, Tl, V, W, Y, Zn, Zr are considered as AFLOW data is much richer in that material domain. A total of 990  $N = 2$ , 14,190  $N = 3$ , and 148,675  $N = 4$  phase diagrams are generated, with 202,261, 974,808, and 432,840 ab-initio entries respectively.

### DATA AVAILABILITY

All the ab-initio data used in this analysis are freely available to the public as part of the AFLOW online repository and can be accessed through AFLOW.org following the REST-API interface<sup>19</sup> and AFLUX search language.<sup>8</sup> The AFLOW source code is available for download at <http://aflow.org> under GNU GPL version 3.

### ACKNOWLEDGEMENTS

The authors thank Ohad Levy for fruitful discussions. Research sponsored by DOD-ONR (N00014-15-1-2863, N00014-16-1-2326, and N00014-17-1-2876).

### AUTHOR CONTRIBUTIONS

S.C. proposed the species-stabilization mechanism. C.T. and C.O. developed the recursive stability codes. D.H. generated the library of  $N = 4$  compounds. All authors discussed the results and contributed to the writing of the article.

### ADDITIONAL INFORMATION

**Competing interests:** The authors declare no competing interests.

**Publisher’s note:** Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

### REFERENCES

- de Fontaine, D. Cluster approach to order–disorder transformations in alloys. In *Solid State Physics*, Vol. 47 (eds Ehrenreich, H. & Turnbull, D.) 33–176 (Academic Press, New York, 1994).
- Bush, T. S., Catlow, C. R. A. & Battle, P. D. Evolutionary programming techniques for predicting inorganic crystal structures. *J. Mater. Chem.* **5**, 1269–1272 (1995).

3. Curtarolo, S. et al. The high-throughput highway to computational materials design. *Nat. Mater.* **12**, 191–201 (2013).
4. Maddox, J. Crystals from first principles. *Nature* **335**, 201 (1988).
5. Gao, M. C. Design of high-entropy alloys. In *High-Entropy Alloys: Fundamentals and Applications* (eds Gao, M. C. et al.) Ch. 11, 369–398 (Springer, Cham, Switzerland, 2016).
6. Widom, M. Frequency estimate for multicomponent crystalline compounds. *J. Stat. Phys.* **167**, 726–734 (2017).
7. Oses, C., Toher, C. & Curtarolo, S. Data-driven design of inorganic materials with the Automatic FLOW framework for materials discovery. *MRS Bull.* **43**, 670–675 (2018).
8. Rose, F. et al. AFLUX: The LUX materials search API for the AFLOW data repositories. *Comput. Mater. Sci.* **137**, 362–370 (2017).
9. Oses, C. et al. AFLOW-CHULL: Cloud-oriented platform for autonomous phase stability analysis. *J. Chem. Inf. Model.* **58**, 2477–2490 (2018).
10. McQuarrie, D. A. *Statistical Mechanics*. (Harper and Row, New York, 1976).
11. Friedrich, R. et al. Coordination corrected ab initio formation enthalpies. *npj Comput. Mater.* **5**, 59 (2019).
12. Rost, C. M. et al. Entropy-stabilized oxides. *Nat. Commun.* **6**, 8485 (2015).
13. Sarker, P., Harrington, T. et al. High-entropy high-hardness metal carbides discovered by entropy descriptors. *Nat. Commun.* **9**, 4980 (2018).
14. Gild, J. et al. High-entropy metal diborides: a new class of high-entropy materials and a new type of ultrahigh temperature ceramics. *Sci. Rep.* **6**, 37946 (2016).
15. Gludovatz, B. et al. A fracture-resistant high-entropy alloy for cryogenic applications. *Science* **345**, 1153–1158 (2014).
16. Li, Z., Pradeep, K. G., Deng, Y., Raabe, D. & Tasan, C. C. Metastable high-entropy dual-phase alloys overcome the strength-ductility trade-off. *Nature* **534**, 227–230 (2016).
17. Braun, J. L. et al. Charge-induced disorder controls the thermal conductivity of entropy-stabilized oxides. *Adv. Mater.* **30**, 1805004 (2018).
18. Balluffi, R. W., Allen, S. M. & Carter, W. C. *Kinetics of Materials*. (John Wiley & Sons, Hoboken, New Jersey, 2005).
19. Taylor, R. H. et al. A RESTful API for exchanging materials data in the AFLOWLIB.org consortium. *Comput. Mater. Sci.* **93**, 178–192 (2014).



**Open Access** This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2019

© 2019. This work is published under <http://creativecommons.org/licenses/by/4.0/>(the “License”). Notwithstanding the ProQuest Terms and Conditions, you may use this content in accordance with the terms of the License.