

AD-A031 515

BATTELLE COLUMBUS LABS OHIO
PREVENTING DELAYED CRACKS IN SHIP WELDS. PART I, (U)
1976 H W MISHLER

F/G 13/5

UNCLASSIFIED

SSC-261

N00024-72-C-5326

NL

1 OF 1
ADA031515



END

DATE
FILMED
12 - 76

AD A031515

SSC-261

12

B.S.

PREVENTING DELAYED CRACKS IN SHIP WELDS

Part I

All 1473

This document has been approved
for public release and sale; its
distribution is unlimited.

DDC
RECEIVED
NOV 3 1976
B

SHIP STRUCTURE COMMITTEE
1976

SHIP STRUCTURE COMMITTEE

AN INTERAGENCY ADVISORY
COMMITTEE DEDICATED TO IMPROVING
THE STRUCTURE OF SHIPS

MEMBER AGENCIES

United States Coast Guard
Naval Sea Systems Command
Military Sealift Command
Maritime Administration
American Bureau of Shipping

ADDRESS CORRESPONDENCE TO

Secretary
Ship Structure Committee
U.S. Coast Guard Headquarters
Washington, D.C. 20590

SR 210

17 AUG 1976

Delayed cracking is a matter of serious concern in some ship weldments.

The Ship Structure Committee undertook a project to prepare a shipyard guide to aid in preventing such cracks. This report contains that guide. It explains in simple and condensed form the causes of delayed cracking and means of prevention. It is intended to be useful for shipyard personnel who do not have a technical background. For this reason detailed technical explanations are avoided.

A technical report containing the background information has been prepared and is published separately as SSC - 262.

W. M. Benkert

Rear Admiral, U. S. Coast Guard
Chairman, Ship Structure Committee

ADMISSION for	
PTIR	White Section <input checked="" type="checkbox"/>
CCC	Buff Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
Dist.	APPL. NO./or SPECIAL
A	

SSC-261

Technical Report

on

Project SR-210, "Delayed Cracking Phenomena"

PREVENTING DELAYED CRACKS IN SHIP WELDS

by

H. W. Mishler

Battelle Columbus Laboratories

under

Department of the Navy
Naval Ship Engineering Center
Contract No. N00024-72-C-5326

*This document has been approved for public release
and sale; its distribution is unlimited.*

U. S. Coast Guard Headquarters
Washington, D.C.
1976

ABSTRACT

Delayed cracking is a continuing problem in ship steel weldments. However, with proper precautions, this type of cracking can be prevented. This document presents, in a simplified and condensed form, the causes of delayed cracking and the necessary preventive procedures. It is intended that this document will be used by shipyard personnel that do not have a technical background. Thus, detailed technical explanations are avoided.

SHIP STRUCTURE COMMITTEE

The SHIP STRUCTURE COMMITTEE is constituted to prosecute a research program to improve the hull structures of ships by an extension of knowledge pertaining to design, materials and methods of fabrication.

RADM W. M. Benkert, USCG
Chief, Office of Merchant Marine Safety
U.S. Coast Guard Headquarters

Mr. P. M. Palermo
Asst. for Structures
Naval Ship Engineering Center
Naval Ship Systems Command

Mr. M. Pitkin
Asst. Administrator for
Commercial Development
Maritime Administration

Mr. K. Morland
Vice President
American Bureau of Shipping

Mr. C. J. Whitestone
Maintenance & Repair Officer
Military Sealift Command

SHIP STRUCTURE SUBCOMMITTEE

The SHIP STRUCTURE SUBCOMMITTEE acts for the Ship Structure Committee on technical matters by providing technical coordination for the determination of goals and objectives of the program, and by evaluating and interpreting the results in terms of ship structural design, construction and operation.

NAVAL SEA SYSTEMS COMMAND

Mr. C. Pohler - Member
Mr. J. B. O'Brien - Contract Administrator
Mr. G. Sorokin - Member

U.S. COAST GUARD

LCDR E. A. Chazal - Secretary
CAPT C. B. Glass - Member
LCDR S. H. Davis - Member
LCDR J. N. Naegle - Member

MARITIME ADMINISTRATION

Mr. N. Hammer - Member
Mr. F. Dashnaw - Member
Mr. F. Seibold - Member
Mr. R. K. Kiss - Member

MILITARY SEALIFT COMMAND

Mr. D. Stein - Member
Mr. T. W. Chapman - Member
Mr. A. B. Stavovy - Member
CDR J. L. Simmons - Member

NATIONAL ACADEMY OF SCIENCES SHIP RESEARCH COMMITTEE

Mr. R. W. Rumke - Liaison
Prof. J. E. Goldberg - Liaison

AMERICAN BUREAU OF SHIPPING

Mr. S. G. Stiansen - Chairman
Mr. I. L. Stern - Member
Dr. H. Y. Jan - Member

SOCIETY OF NAVAL ARCHITECTS & MARINE ENGINEERS

Mr. A. B. Stavovy - Liaison

WELDING RESEARCH COUNCIL

Mr. K. H. Koopman - Liaison

INTERNATIONAL SHIP STRUCTURES CONGRESS

Prof. J. H. Evans - Liaison

U.S. COAST GUARD ACADEMY

CAPT W. C. Nolan - Liaison

STATE UNIV. OF N.Y. MARITIME COLLEGE

Dr. W. R. Porter - Liaison

AMERICAN IRON & STEEL INSTITUTE

Mr. R. H. Sterne - Liaison

U.S. NAVAL ACADEMY

Dr. R. Bhattacharyya - Liaison

NOTES

PREVENTING DELAYED CRACKS IN SHIP WELDS

WHAT IS A DELAYED CRACK ? WHY IS IT BAD ?

A weld joint that appears to be perfectly sound sometimes has the uncanny ability to develop internal cracks after welding is completed. These cracks may form several hours or maybe even days after the weld is made, inspected, and given a clean bill of health. Because it takes time for these cracks to develop, they are called "delayed cracks".

When welds containing delayed cracks are stressed during service, the weld may fail with a considerable financial loss or even personal injury or loss of life. Thus, it is very important that every step be taken to prevent the formation of delayed weld cracks.

**DELAYED WELD CRACKS
CAN BE THE CAUSE
OF DELAYED FAILURES**



Delayed cracks sometimes are called underbead cracks. This is because the crack actually is in the heat-affected zone just under or at the side of the weld bead. Like as not, the crack doesn't come to the surface so, it can't be seen. Since the crack occurs after the weld is completed and isn't visible, you can be using procedures that cause delayed cracks and not even know it. Fortunately, though, procedures have been worked out that will prevent this cracking if they are followed properly.



THIS IS WHAT A DELAYED CRACK LOOKS LIKE WHEN THE WELD IS CUT APART

To understand why these procedures are important, it helps to know -

WHAT CAUSES DELAYED CRACKS ?

Three conditions are necessary to cause a delayed crack. All three must be present simultaneously.

They are:

1. Hydrogen dissolved in the weld metal
2. A hard structure in the heat-affected zone
3. Stresses in the weld joint.



THE REQUIREMENTS FOR DELAYED CRACKS

Hydrogen dissolves in the weld while the weld metal still is molten. This hydrogen can come from a variety of sources. The most common is moisture or organic material in the electrode covering or coating. Both moisture and organic materials contain hydrogen. The arc breaks down these hydrogen compounds to provide free hydrogen which dissolves in the weld.

Two types of electrode coatings are made:

1. Those that contain organic materials or hydrogen-containing binders. These are the electrodes that have the following numbers in their designation:

E-XX10 E-XX12 E-XX14 E-XX24
E-XX11 E-XX13 E-XX20 E-XX27

2. Those that do not contain organic or hydrogen-containing materials. These are called "low-hydrogen" electrodes. Only those electrodes that have the following designations are low-hydrogen electrodes:

E-XX15 E-XX18
E-XX16 E-XX28

The low-hydrogen electrodes still can have moisture in their coatings if they aren't handled properly -- more about this later. Hydrogen can also come from any hydrogen compounds or moisture that gets into the arc. Some of these are listed over on the right.

Some steels, when welded, will form a hard microstructure in the heat-affected zone next to the weld. This is where the dissolved hydrogen will finally settle and cause the delayed cracks. As a rule of thumb, you can say that the higher

SOURCES OF HYDROGEN

- Electrodes with hydrogen-containing coatings, such as
E6010 E6011
E7024 E6027
- Moisture in electrode coatings
- Moisture on joint surfaces
- Foreign matter on electrodes (grease, food, oil, paint, perspiration)
- Foreign matter on joint surfaces (oil, rust, paint, grease, dirt, crayon markings)


the strength of the steel, the more likely it will have the hard microstructure after welding. Unfortunately, you can't tell if this hard structure has formed just by looking at the joint. To see this structure, a piece must be cut from the weld, polished, etched, and looked at under a microscope. This hard microstructure forms only when the hot metal cools too fast. Therefore, any welding practice that speeds up cooling will increase the probability of forming the hard microstructure. Any procedure that keeps the amount of heat generated in the weld joint low will also increase the cooling rate of the joint. Some of these "low-heat" procedures would include:

- low welding heat (low-current)
- fast travel
- no preheat
- low interpass temperature
- small electrodes



**FAST COOLING IS
NEEDED TO FORM THE
HARD MICROSTRUCTURE**


The lower strength steels require such a fast cooling rate to form the hard microstructure that the weld would have to be artificially cooled (quenching in water, for example). Under the cooling rates normal to welding, the hard microstructure does not usually form in weld joints in such low-strength steels as ABS Grades A, B, D, DS, CS, or E. Some hard microstructure may form in higher strength steels, though, at these cooling rates.

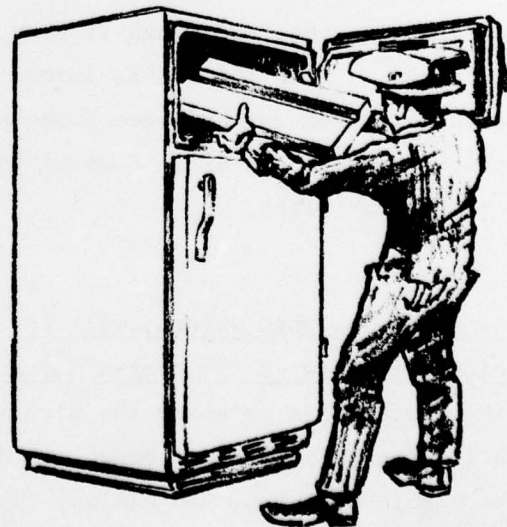

Stresses are created in all weld joints from the shrinkage of the weld as it cools. Forcing plates into alignment, lifting or moving a partially welded assembly or the unsupported weight of the parts being welded will add to these stresses. However, the shrinkage stresses alone may be enough to cause delayed cracking in the higher strength steels if hydrogen is present.



Sometimes delayed cracks will occur near an abrupt change in weld shape even though the overall stresses are too low to cause cracking. This is because stresses will build up around the shape change. That's why these shape changes are called "stress raisers". Typical stress raisers are undercutting, overlap, lack of fusion of the weld root, elongated slag inclusions, or a sharp change in contour due to poor fitup. These stress raisers have a major effect on the formation of delayed cracks.

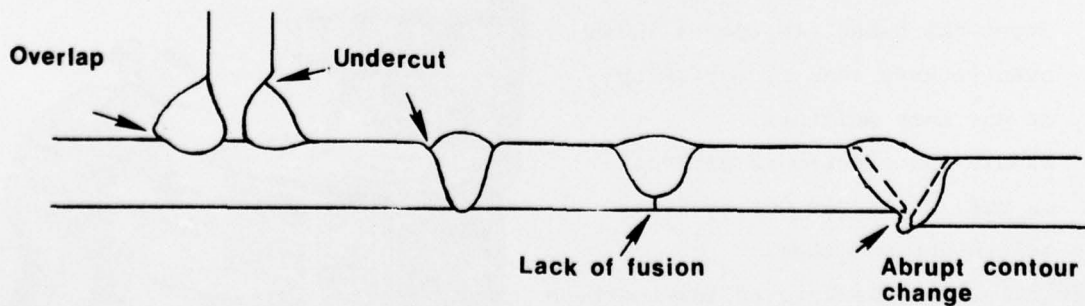

**SOME STRESS RAISERS THAT CAN CAUSE
HIGH STRESSES IN LOCALIZED AREAS**

HOW TO PREVENT DELAYED CRACKS

First, check to see if the steel to be welded is susceptible to delayed cracking. The lowest strength steels used in shipbuilding are ABS-A, ABS-B, and ABS-C. Delayed cracking won't occur in welds involving only these steels so they can be welded without any special precautions, other than good welding practice. Special precautions, though, are needed when welding any of the higher-strength steels. These precautions eliminate or minimize the three factors that cause delayed cracking. The three rules described in pages 6 through 9 cover these precautions.

The first
rule is




GET RID OF THE HYDROGEN

If you follow this basic rule, many delayed cracking problems will be solved. This is done quite simply by using properly dried low-hydrogen electrodes, keeping the joint clean, and preheating.

Low-hydrogen electrodes have the numbers 15, 16, 18, or 28 in their designation - for example, E8016 or E11018. However, these electrodes must be treated properly since they'll quickly pick up moisture from the air and then they won't be low-hydrogen electrodes. The proper treatment for low-hydrogen electrodes is:

- (1) Bake new electrodes to drive off any moisture left in the electrodes after they were made.
- (2) Store the baked electrodes in an oven to keep them from picking up any more moisture.
- (3) Handle the electrodes correctly so they won't get wet or dirty before you use them.

Specific rules for the care of low-hydrogen electrodes are given on page 11 at the end of this manual.

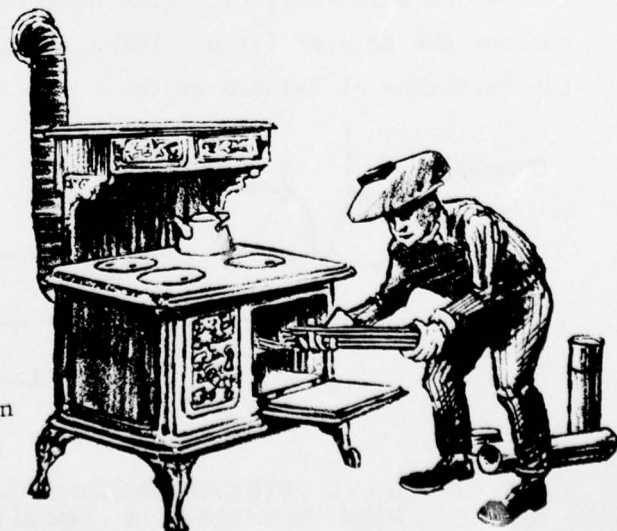


The joint should be clean before welding. There shouldn't be any grease, rust, dirt, paint or crayon markings on the joint faces when you start to weld. Wire brush or grind the joint surfaces to remove foreign matter. If you measure preheating or interpass temperatures with heat sensitive crayons, make the crayon marks on the base-plate surface, not on the joint surface.



Cleanliness is next to

At night, moisture can condense on joint faces. The best way of getting rid of this source of hydrogen is to dry the joints by preheating them. If the temperature gets up to 75° - 85° during the day, this moisture will evaporate. Until this temperature is reached, the joints should be heated until they are hot to the touch.

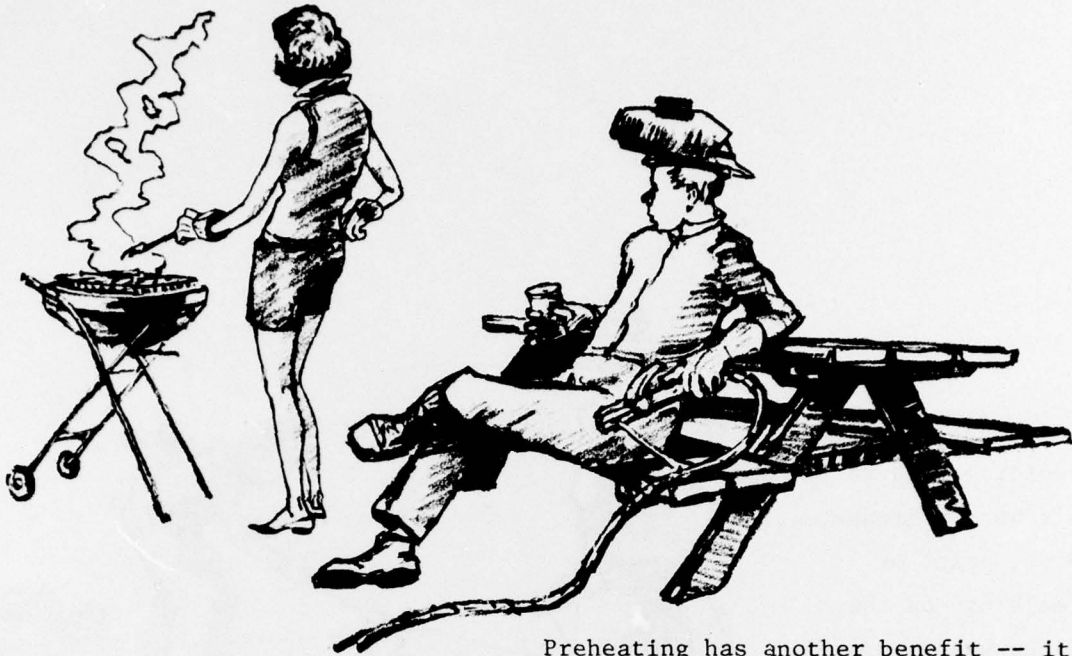

The second
rule is



**PREVENT
FORMATION
OF A HARD
MICROSTRUCTURE**

Preheating has another benefit -- it slows down the cooling rate of a joint after it is welded. This slower cooling will reduce the tendency for formation of a hard microstructure in the heat-affected zone. (Preheating also helps the hydrogen to diffuse out of the joint.) Interpass temperatures must be kept above the same level since the interpass temperature is somewhat the same as preheating. If the interpass temperature gets below the specified level, heat the joint up again before doing any more welding.

Preheat and interpass temperatures usually fall into the range of 75^o-250^oF. The temperature actually used, however, will be governed by the steel composition and thickness. The temperature to be used will be designated in the welding specification covering your job.

Special care is required with quenched and tempered steels. If these steels cool too slowly after welding, they will lose strength and toughness. Since preheating acts to slow down this cooling rate, these steels mustn't be preheated too high. A maximum limit of 300^oF generally is set on the preheat and interpass temperature for these steels.


The first two factors causing delayed cracking, hydrogen and hard microstructure, can be eliminated through the use of proper procedures. The third factor, high stresses, can only be reduced - stresses can never be completely eliminated. Getting rid of hydrogen and the hard microstructure generally will prevent delayed cracking even if high stresses remain. However, every little bit helps, so steps also should be taken to keep stresses down.

The third
rule is



**MINIMIZE
STRESSES**

This is not always easy to do but there are a couple of precautions that are helpful. First, try to maintain good alignment of the parts. This means lining up the parts correctly before tack welding with as little forcing as possible. Forcing just increases the joint stresses. Second, use welding procedures that will avoid the formation of stress raisers. Good alignment helps here, too. Especially important is the prevention of undercutting, lack of fusion, and abrupt contour changes. Third, use pre-heating and hold interpass temperature if more than one pass is to be made. A slower cooling rate helps reduce shrinkage stresses. And fourth, if possible, weld long joints from the center of the joint toward the joint ends. This technique will provide a more even distribution of shrinkage stresses.

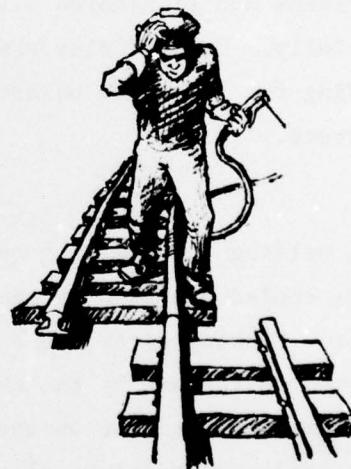

**Good alignment sure
helps reduce stresses.**



**There are some other
ways that help too**

OTHER WELDING PROCESSES

Only stick or covered electrode welding has been considered so far. Delayed cracks can occur in MIG, flux-cored wire, or submerged-arc welding, too. The precautions to prevent or minimize delayed cracking, though, are basically the same. The only real difference is in the methods used to eliminate hydrogen. These are different only because some of the welding materials are different.

The electrode wires (both solid and flux-cored) and submerged-arc fluxes must be kept clean and dry. Each manufacturer has recommended rules for the care and storage of fluxes and flux-cored wires. These should be followed carefully. Unfused flux should not be reclaimed from welding for later use unless it is rebaked to remove moisture.

Keep welding torches in good repair. If the torches are water cooled, be sure fittings are tight and not leaking water. Leaking water could drip onto the joint or be carried to the arc by the shielding gas. In humid weather, moisture can condense on the parts of a water cooled torch. This condensed moisture also can drip or be carried into the weld area. Watch out for these moisture sources.

The other precautions relating to preheat and interpass temperatures, cleaning, stresses, etc., apply unchanged when MIG, flux-cored wire, or submerged-arc welding are used.

RULES FOR CARE OF LOW HYDROGEN ELECTRODES

1. If the electrodes are in an airtight metal container, immediately upon opening the container place the electrodes in a ventilated holding oven set at 250^o-300^oF.
2. If the electrode can is not airtight (check for damage to can) or if the container is a cardboard box, put electrodes in a baking oven. Check with electrode vendor for correct baking temperature and time.
3. Transfer electrodes while still hot to a holding oven kept at a temperature of 250^oF - 300^oF. Keep electrodes in this oven until ready to use.
4. A supply of electrodes for welding should be kept in a portable heated electrode container at the welding site, if possible.
5. If a heated electrode container is not available, electrodes removed from the holding oven should be used within the following times:

E-70XX	4 hours
E-80XX	2 hours
E-90XX	1 hour
E-110XX	1/2 hour

Sometimes E-70XX and E-80XX electrodes are substituted for E-90XX or E-110XX electrodes for tack or root-pass welding. In these cases, the electrodes should be baked to reduce their moisture content to the level of E-90XX and E-110XX electrodes and the maximum exposure times should be reduced to 1/2 hours.

6. Any electrodes unused at the end of these times or any electrodes remaining in a heated electrode holder at the end of 4 hours should not be returned to the holding oven. These electrodes should be rebaked as specified in Rule 2.
7. Electrodes should be rebaked only once. Electrodes requiring a second rebaking should be discarded.
8. Any electrodes exposed to rain or snow or perspiration, that get wet for any reason, that get dirty or pick up oil, grease, or any other contaminating material should be discarded at once.

Note: These rules are intended to insure dry electrodes under most unfavorable environments. They may be relaxed or made more restrictive by a shipyard to meet its specific needs.

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 18 SSC 261	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Preventing Delayed Cracks in Ship Welds • Part I,	5. TYPE OF REPORT & PERIOD COVERED	
7. AUTHOR(s) H. W. Mishler	6. PERFORMING ORG. REPORT NUMBER	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Battelle-Columbus Laboratories ✓ 505 King Avenue Columbus, Ohio 43201	8. CONTRACT OR GRANT NUMBER(s) Contract N00024-72-C-5326 15	
11. CONTROLLING OFFICE NAME AND ADDRESS Department of the Navy Naval Ship Systems Command Washington, D. C. 20360	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS SR-210	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 12 18P	12. REPORT DATE 11 1976	
	13. NUMBER OF PAGES 11	
	15. SECURITY CLASS. (of this report) Unclassified	
15a. DECLASSIFICATION/DOWNGRADING SCHEDULE		
16. DISTRIBUTION STATEMENT (of this Report) Distribution of this document is unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) Unlimited		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Welding Cold cracking Weld cracking Shipbuilding Steels Hydrogen cracking		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Delayed cracking is a continuing problem in ship steel weldments. However, with proper precautions, this type of cracking can be prevented. This document presents, in a simplified and condensed form, the causes of delayed cracking and the necessary preventive procedures. It is intended that this document will be used by shipyard personnel that do not have a technical background. Thus, detailed technical explanations are avoided.		

DD FORM 1473 1 JAN 73 EDITION OF 1 NOV 65 IS OBSOLETE

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

407080 LB

SHIP RESEARCH COMMITTEE
Maritime Transportation Research Board
National Academy of Sciences-National Research Council

The Ship Research Committee has technical cognizance of the inter-agency Ship Structure Committee's research program:

PROF. J. E. GOLDBERG, Chairman, *School of Civil Engineering, Purdue University*
PROF. R. W. CLOUGH, *Prof. of Civil Engineering, University of California*
DR. S. R. HELLER, Jr., *C'man, Civil & Mech. Eng. Dept., The Catholic Univ. of America*
MR. G. E. KAMPSCHAEFER, Jr., *Manager, Technical Services, ARMCO Steel Corporation*
MR. W. W. OFFNER, *Consulting Engineer, San Francisco*
MR. D. P. ROSEMAN, *Chief Naval Architect, Hydronautics, Inc.*
MR. H. S. TOWNSEND, *Vice President, U.S. Salvage Association, Inc.*
DR. S. YUKAWA, *Consulting Engineer, General Electric Company*
MR. R. W. RUMKE, *Executive Secretary, Ship Research Committee*

Advisory Group III, "Materials, Fabrication, and Inspection", prepared the project prospectus and evaluated the proposals for this project:

MR. G. E. KAMPSCHAEFER, Jr., Chairman, *Manager, Tech. Services, ARMCO Steel Corp.*
DR. J. M. BARSOM, *Research Consultant, U.S. Steel Corporation*
PROF. J. R. FREDERICK, *Dept. of Mech. Engineering, The University of Michigan*
MR. S. GOLDSPIEL, *Mechanical Engineer, Board of Water Supply, New York*
MR. T. E. KOSTER, *Naval Architect, AMOCO International Oil Company*
DR. J. M. KRAFFT, *Head, Ocean Materials Criteria Branch, Naval Research Lab.*
MR. G. E. LINNERT, *North American Representative, The Welding Institute*
PROF. H. W. LIU, *Professor of Materials Science, Syracuse University*
PROF. W. H. MUNSE, *Dept. of Civil Engineering, University of Illinois*
MR. W. W. OFFNER, *Consulting Engineer, San Francisco*
PROF. H. C. ROGERS, *College of Engineering, Drexel University*
DR. W. F. SAVAGE, *Professor of Metallurgy, Rensselaer Polytechnic Institute*
DR. W. K. WILSON, *Analytical Mechanics, Westinghouse Electric Corporation*

The SR-210 Project Advisory Committee provided the liaison technical guidance, and reviewed the project reports with the investigator:

Prof. A. W. Pense, Chairman, *Prof. of Metallurgy, Lehigh University*
Mr. G. E. Linnert, *N. American Representative, The Welding Institute*

SHIP STRUCTURE COMMITTEE PUBLICATIONS

These documents are distributed by the National Technical Information Service, Springfield, Va. 22151. These documents have been announced in the Clearinghouse journal U.S. Government Research & Development Reports (USGRDR) under the indicated AD numbers.

- SSC-253, *A Guide for the Nondestructive Testing of Non-Butt Welds in Commercial Ships - Part One* by R. A. Youshaw and E. L. Criscuolo. 1976. AD-A014547.
- SSC-254, *A Guide for the Nondestructive Testing of Non-Butt Welds in Commercial Ships - Part Two* by R. A. Youshaw and E. L. Criscuolo. 1976. AD-A014548.
- SSC-255, *Further Analysis of Slamming Data from the S.S. WOLVERINE STATE* by J. W. Wheaton. 1976. AD-A021338.
- SSC-256, *Dynamic Crack Propagation and Arrest in Structural Steels* by G. T. Hahn, R. G. Hoagland, and A. R. Rosenfield. 1976. AD-A021339.
- SSC-257, *SL-7 Instrumentation Program Background and Research Plan* by W. J. Siekierka, R. A. Johnson, and CDR C. S. Loosmore, USCG. 1976. AD-A021337.
- SSC-258, *A Study To Obtain Verification of Liquid Natural Gas (LNG) Tank Loading Criteria* by R. L. Bass, J. C. Hokanson, and P. A. Cox. 1976.
- SSC-259, *Verification of the Rigid Vinyl Modeling Technique: The SL-7 Structure* by J. L. Rodd. 1976.
- SSC-260, *A Survey of Fastening Techniques for Shipbuilding* by N. Yutani and T. L. Reynolds. 1976.

SL-7 PUBLICATIONS TO DATE

- SL-7-1, (SSC-238) - *Design and Installation of a Ship Response Instrumentation System Aboard the SL-7 Class Containership S.S. SEA-LAND McLEAN* by R. A. Fain. 1974. AD 780090.
- SL-7-2, (SSC-239) - *Wave Loads in a Model of the SL-7 Containership Running at Oblique Headings in Regular Waves* by J. F. Dalzell and M. J. Chiocco. 1974. AD 780065.
- SL-7-3, (SSC-243) - *Structural Analysis of SL-7 Containership Under Combined Loading of Vertical, Lateral and Torsional Moments Using Finite Element Techniques* by A. M. Elbatouti, D. Liu, and H. Y. Jan. 1974. AD-A 002620.
- SL-7-4, (SSC-246), *Theoretical Estimates of Wave Loads on the SL-7 Containership in Regular and Irregular Seas* by P. Kaplan, T. P. Sargent, and J. Cilmi. 1974. AD-A 004554.
- SL-7-5, (SSC-257) - *SL-7 Instrumentation Program Background and Research Plan* by W. J. Siekierka, R. A. Johnson, and CDR C. S. Loosmore, USCG. 1976. AD-A021337.
- SL-7-6, (SSC-259) - *Verification of the Rigid Vinyl Modeling Technique: The SL-7 Structure* by J. L. Rodd. 1976.