

AD-A034 661

NAVAL AIR DEVELOPMENT CENTER WARMINSTER PA AIR VEHICL--ETC F/G 11/6  
INDEXING THE DEGREE OF HYDROGEN EMBRITTLEMENT OF 4340 STEEL USI--ETC(U)  
NOV 76 D A BERMAN

UNCLASSIFIED

NADC-76359-30

NL

| OF |

AD  
A034661



END

DATE  
FILMED  
2-77



ADA034661

REPORT NO. NADC-76359-30



INDEXING THE DEGREE OF HYDROGEN EMBRITTLEMENT OF  
4340 STEEL USING THE BARNACLE ELECTRODE.

D. A. Berman

Air Vehicle Technology Department  
NAVAL AIR DEVELOPMENT CENTER  
Warminster, Pennsylvania 18974

3 NOVEMBER 1976

PROGRESS REPORT

AIRTASK NO. R 0220 T01  
Work Unit No. DG 202



APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

Prepared for  
NAVAL AIR SYSTEMS COMMAND  
Department of the Navy  
Washington, D.C. 20361

1473  
407207 LB

## NOTICES

**REPORT NUMBERING SYSTEM** - The numbering of technical project reports issued by the Naval Air Development Center is arranged for specific identification purposes. Each number consists of the Center acronym, the calendar year in which the number was assigned, the sequence number of the report within the specific calendar year, and the official 2-digit correspondence code of the Command Office or the Functional Department responsible for the report. For example: Report No. NADC-76015-40 indicates the fifteenth Center report for the year 1976, and prepared by the Crew Systems Department. The numerical codes are as follows:

CODE	OFFICE OR DEPARTMENT
00	Commander, Naval Air Development Center
01	Technical Director, Naval Air Development Center
02	Program and Financial Management Department
09	Technology Management Office
10	Naval Air Facility, Warminster
20	Aero Electronic Technology Department
30	Air Vehicle Technology Department
40	Crew Systems Department
50	Systems Department
60	Naval Navigation Laboratory
81	Technical Support Department
85	Computer Department

**PRODUCT ENDORSEMENT** - The discussion or instructions concerning commercial products herein do not constitute an endorsement by the Government nor do they convey or imply the license or right to use such products.

APPROVED BY:

*P. M. Sturm*  
 P. M. STURM  
 Commander, USN  
 Deputy Director, AVTD

DATE: 3 NOV 76



# UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle)  INDEXING THE DEGREE OF HYDROGEN EMBRITTLEMENT OF 4340 STEEL USING THE BARNACLE ELECTRODE		5. TYPE OF REPORT & PERIOD COVERED  PROGRESS
7. AUTHOR(s)  D. A. BERMAN		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Naval Air Development Center Air Vehicle Technology Department ✓ Warminster, Pennsylvania 18974		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS AIRTASK NO. R 0220 101 Work Unit No. DG 202
11. CONTROLLING OFFICE NAME AND ADDRESS Naval Air Systems Command Department of the Navy Washington, DC 20361		12. REPORT DATE 3 NOV 76
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		13. NUMBER OF PAGES 17
		15. SECURITY CLASS. (of this report)  UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report)  Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)  Hydrogen embrittlement                      Sustained load testing Hydrogen detection                            4340 steel Barnacle electrode Electrochemical technique		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number)  The barnacle electrode, an electrochemical device based on the hydrogen permeation method, was used, in conjunction with sustained load tests, to index the degree of embrittlement of 4340 steel. Flat, double notched tensile specimens of 250 ksi (1725 MPa) notched tensile strength and having a $K_t$ of 5.6 were shown to have a critical diffusible hydrogen concentration of 1.9, 1.7, 1.4, 1.2, 0.9 and 0.5 ppm for loads of 15, 20, 25, 30, 35 and 40 percent of the notched tensile strength.		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE  
S/N 0102-014-6601

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

K sub T

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

[Empty rectangular box for content]

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

## S U M M A R Y

## INTRODUCTION

The phenomenon of hydrogen entering high strength steels, such as the landing gear of Naval aircraft, causing catastrophic failure when under stress is a well known problem. It is important, therefore, to know the hydrogen concentrations that a part can contain without failing at service loads, and to be able to measure this hydrogen. In the course of development experiments with the barnacle electrode system, an electrochemical device for the in situ measurement of embrittling mobile hydrogen in high strength steels, it was found that a critical hydrogen concentration for cracking of 4340 steel appeared to exist at given stress levels. Therefore, this study was undertaken to index the degree of embrittlement in this alloy over a range of stresses, as well as to determine critical concentrations. This project was authorized by the Naval Air Systems Command and was carried out as part of the ongoing research on corrosion and corrosion resistant materials, AIRTASK No. R 0220 101, Work Unit No. DG 202.

## SUMMARY OF RESULTS

Flat, double notched tensile specimens of AISI 4340 steel of 250 ksi (1725 MPa) notched tensile strength and having a  $K_t$  of 5.6 were shown to have critical diffusible hydrogen concentrations of 1.9, 1.7, 1.4, 1.2, 0.9 and 0.5 ppm for sustained loads of 15, 20, 25, 30, 35 and 40 percent of the notched tensile strength (NTS).

## CONCLUSIONS

It was shown that it is possible to index the degree of hydrogen embrittlement of a high strength steel with the barnacle electrode; that hydrogen concentrations as low as 0.5 ppm can be determined; that these low levels of hydrogen can be embrittling; and that the barnacle electrode measuring time can be reduced from thirty to twenty minutes.

TABLE OF CONTENTS

	<u>Page No.</u>
SUMMARY	
Introduction . . . . .	1
Summary of Results . . . . .	1
Conclusions. . . . .	1
LIST OF TABLES . . . . .	3
LIST OF FIGURES . . . . .	3
BACKGROUND. . . . .	4
EXPERIMENTAL PROCEDURES . . . . .	5
RESULTS AND DISCUSSION. . . . .	8
CONCLUSIONS . . . . .	14
ACKNOWLEDGEMENTS. . . . .	14
REFERENCES. . . . .	15



## LIST OF TABLES

<u>Table No.</u>		<u>Page No.</u>
I	Critical Hydrogen Concentration for Failure of AISI 4340 Steel in Sustained Load Testing. $K_t = 5.6$ , NTS = 250 ksi. . . . .	8
II	Calculated Hydrogen Concentrations (ppm) from Barnacle Electrode Measurements at Selected Extraction Times . . . . .	13

## LIST OF FIGURES

<u>Figure No.</u>		
1.	Barnacle Electrode Measuring Apparatus . . . . .	6
2.	Schematic of Barnacle Electrode Measuring Apparatus. . . . .	7
3.	Typical Barnacle Electrode Hydrogen Extraction Transients. . . . .	9
4.	Indexing the Degree of Hydrogen Embrittlement of AISI 4340 Steel Using Thirty-Minute Barnacle Electrode Measurements. . . . .	10
5.	Indexing the Degree of Hydrogen Embrittlement of AISI 4340 Steel Using Twenty-Minute Barnacle Electrode Measurements. . . . .	11
6.	Barnacle Electrode Hydrogen Extraction Transients versus Theoretical Curves Calculated from Equation (1) for AISI 4340 Steel, $D = 2.5 \times 10^{-7} \text{ cm}^2\text{s}^{-1}$ . . . . .	12



## B A C K G R O U N D

It is well known that hydrogen can enter high strength steels in many ways causing a loss in ductility which may result in catastrophic failure. This hydrogen can exist in a very low concentration in the steel and yet cause damage because the hydrogen in a metal under stress migrates to areas of high stress intensity, magnifying its effect (references (a), (b) and (c)).

The barnacle electrode is being developed by the Aeronautical Materials Laboratory as a device intended for the in situ measurement of embrittling mobile hydrogen in high strength steel parts. The principle of the barnacle electrode is based on the electrochemical coulometric method of hydrogen permeation and is described elsewhere (references (d) and (e)).

In the course of laboratory experiments with the barnacle electrode system, it was found that a critical concentration for mobile hydrogen to cause cracking of 4340 steel appeared to exist for the stress level used (reference (d)). It therefore seemed advisable to investigate this system more fully in order to index the degree of embrittlement over a range of stresses, as well as to confirm the existence of this critical concentration.

Devanathan and Stachurski (references (f) and (g)) were the first to use a very sensitive electrochemical technique to measure the rate of permeation of hydrogen through thin metal membranes. This method requires that a diffusion gradient exist within the metal foil by producing hydrogen on one side, e.g., by cathodic charging, and removing it on the other side by anodic polarization with a potentiostat. By keeping the exit surface at zero hydrogen concentration in this manner, the oxidizing current is, therefore, a direct indication (through Faraday's law) of the rate of diffusion of hydrogen. Analysis of the build-up and decay transients can then be used to give diffusivity/concentration information (references (d), (e) and (h)).

The barnacle electrode technique makes use of only the anodic side of the permeation cell. A nickel/nickel oxide electrode replaces the potentiostat to create and maintain the potential to extract and oxidize the hydrogen (which is uniformly distributed throughout the specimen) and thus maintain zero hydrogen concentration at the exit surface of the specimen. The boundary conditions are thus established for solution of the diffusion equations (references (d) and (h)). The first term Laplace transform solution according to Gileadi (reference (h)) is given by equation (1)

$$C_o = \frac{J}{ZF} \left( \frac{\pi t}{D} \right)^{\frac{1}{2}} \quad (1)$$

where  $C_o$  = concentration of hydrogen

$J$  = oxidation current density

$F$  = Faraday

$Z$  = number of electrons in oxidation reaction

$t$  = time

$D$  = diffusivity

$\text{mol cm}^{-3}$

$\text{A cm}^{-2}$

$96500 \text{ C mol}^{-1}$

$\text{s}^2 \text{ cm}^{-1} \text{ s}^{-1}$

If the experimental extraction current-time transient fits the curves calculated from the above equation, and if the diffusivity of hydrogen through the given steel is known, a measurement of  $J$  for any given time will give the hydrogen content,  $C_0$ .

The degree of embrittlement is a function, not only of the hydrogen concentration, but also of the material, including its heat treatment and its geometry which determines the stress concentration factor,  $K_t$ . It is, therefore, necessary to do mechanical testing and correlate failure data with the electrochemical measurements for the material of interest.

#### EXPERIMENTAL PROCEDURES

The specimens used in this study were double notched, 0.063 inch (1.60 mm) thick tensile bars of AISI 4340 steel having a notched tensile strength of 250 ksi (1725 MPa) and a  $K_t$  of 5.6. They were finished by surface grinding, then swabbed with 2 percent aqueous HCl in methanol, rinsed with methanol, and wiped with a Kimwipe just prior to charging.

Hydrogen was introduced by cathodic charging of the entire specimen for three hours at a constant current in a solution containing one percent each of NaOH and NaCN, the latter acting as a poison to promote hydrogen uptake (reference (1)). The charging rate (i.e., current density) was varied to provide different hydrogen levels. The anode was a cylindrical platinum gauze surrounding the specimen.

After charging, the specimen was rinsed with de-ionized water followed by a methanol rinse and dried with a Kimwipe. The barnacle electrode was then assembled and measurements taken within 15 minutes of charging using 0.2 M NaOH as electrolyte.

After the thirty-minute barnacle measurement, the specimen was rinsed with water and dried, then stressed in a constant load stress rupture machine. Specimens still intact after one week were considered unembrittled. Failure usually occurred within one-half hour. Thus, a fail-no fail criterion was established.

The barnacle cell consists of a hollow Teflon block which has a 1.0 cm<sup>2</sup> circular opening which fits against the specimen. The contact surface is a raised rim of approximately 4 mm diameter which provides a pressure fit when the clamp is tightened. As extra assurance for a sharp, reproducible solution contact area, a replaceable, 0.1 mm thick Teflon gasket is glued to this rim with rubber cement. The cell is clamped to the specimen with a special C-clamp which has a thumbscrew for tightening. The nickel/nickel oxide electrode is a piece of nickel/cadmium battery positive plate having a nickel contact strip.

The complete setup is shown pictorially and schematically in Figures 1 and 2, respectively.

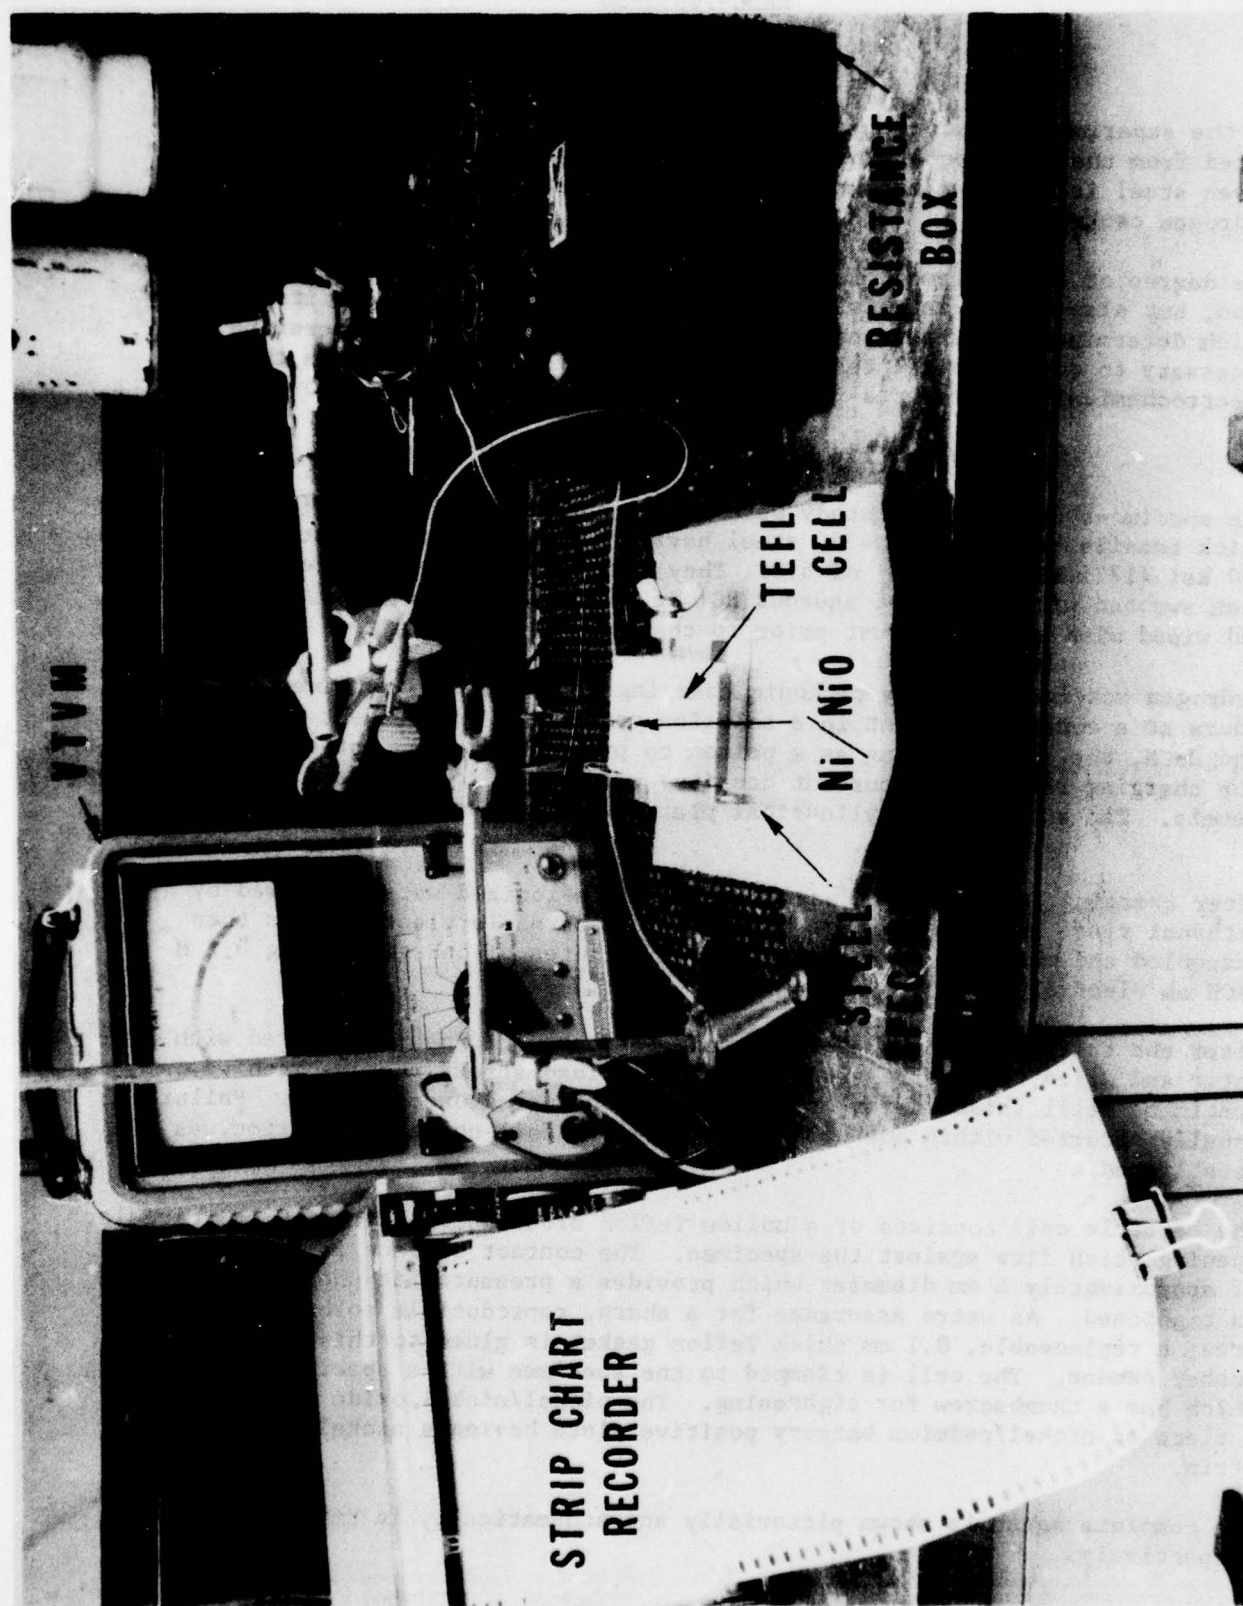


Figure 1. Barnacle Electrode Measuring Apparatus



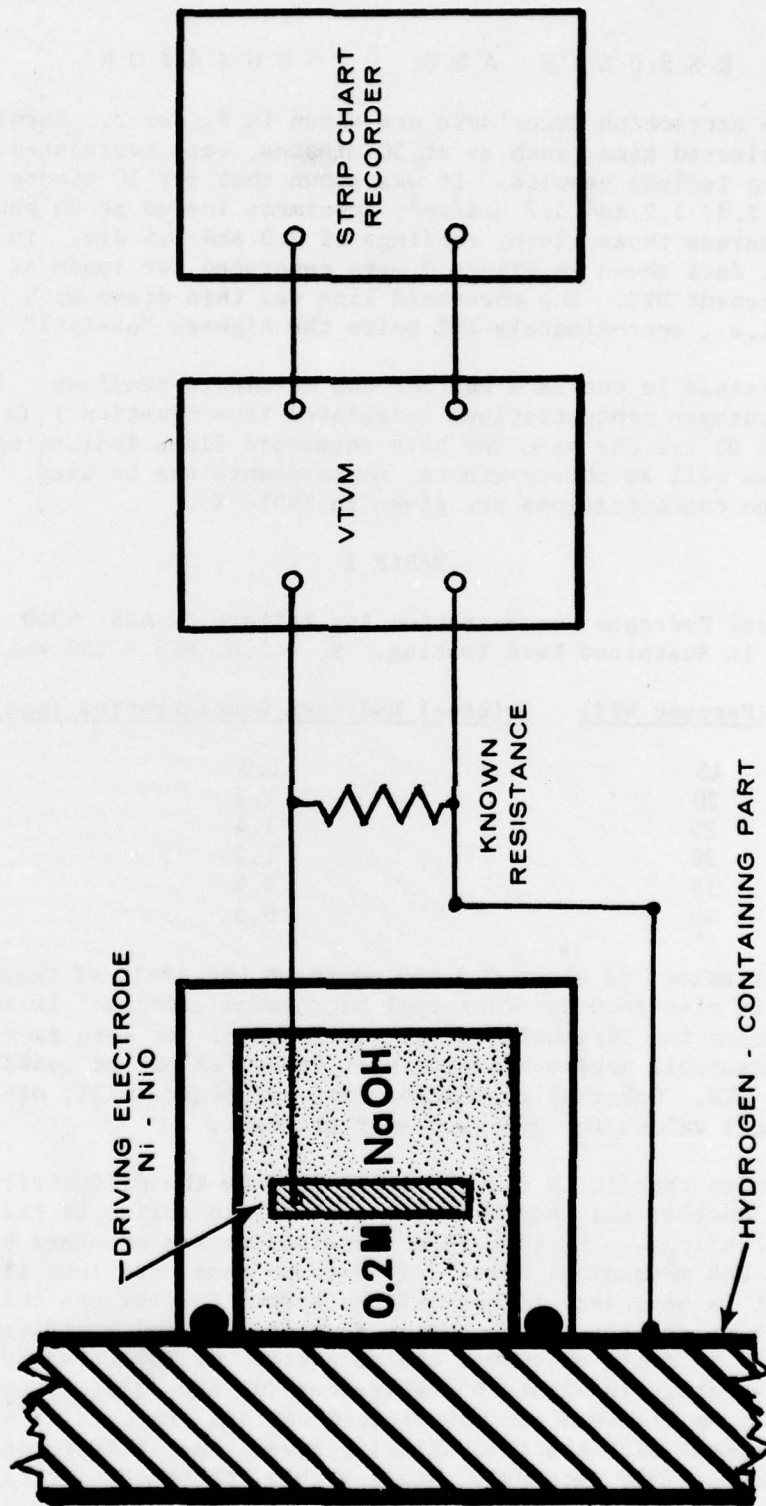


Figure 2. Schematic of Barnacle Electrode Measuring Apparatus

## RESULTS AND DISCUSSION

Typical barnacle extraction transients are shown in Figure 3. Barnacle readings at a selected time, such as at 30 minutes, were correlated with sustained loading failure results. It was shown that for 30-minute barnacle measurements of 2.8, 5.2 and 5.7  $\mu\text{A}/\text{cm}^2$ , specimens loaded at 25 percent NTS did not fail, whereas those giving readings of 7.0 and 7.4 did. In this way, the fail-no fail data shown in Figure 3 were generated for loads of 15, 20, 25, 30 and 40 percent NTS. The threshold line was then drawn with a 10 percent safety factor; i.e., approximately 10% below the highest "no-fail" points.

Figure 4 was obtained in the same way for the 20-minute readings. It can be seen that the hydrogen concentrations calculated from Equation 1 (right hand axes in Figures 4 and 5) are the same for both threshold lines indicating that twenty-minute, as well as thirty-minute, measurements can be used. These critical hydrogen concentrations are given in Table I.

TABLE I

Critical Hydrogen Concentration for Failure of AISI 4340  
Steel in Sustained Load Testing.  $K_t = 5.6$ , NTS = 250 ksi

<u>Load (Percent NTS)</u>	<u>Critical Hydrogen Concentration (ppm)</u>
15	1.9
20	1.7
25	1.4
30	1.2
35	0.9
40	0.5

Hydrogen concentrations of about 0.5 ppm approach the limit of measurement with the barnacle electrode due to normal background effects. It is unnecessary to extend the threshold curves any further. As seen from Figures 4 and 5, any measurable mobile hydrogen will cause failure at loads greater than 40 percent NTS. Other alloys and/or heat treatments will, of course, give different critical values for hydrogen embrittlement.

The foregoing shows that it is not necessary to know the diffusivity of hydrogen in the steel or whether this system follows theory to arrive at threshold barnacle values as long as reproducible correlations are obtained between the electrochemical and mechanical data. If hydrogen concentrations are desired, however, then it is necessary to know if the system follows the theoretical equation (Eq. 1) at various times. Using Equation (1) and a diffusivity of  $2.5 \times 10^{-7} \text{ cm}^2\text{s}^{-1}$  a family of curves can be plotted for selected hydrogen concentrations as shown in Figure 6 (references (d) and (j)). If the extraction transients from Figure 3 are now plotted on this graph it is seen that they are in good agreement with the theoretical curves, especially for times in excess of 15 minutes (900 seconds). Knowing this, these theoretical curves



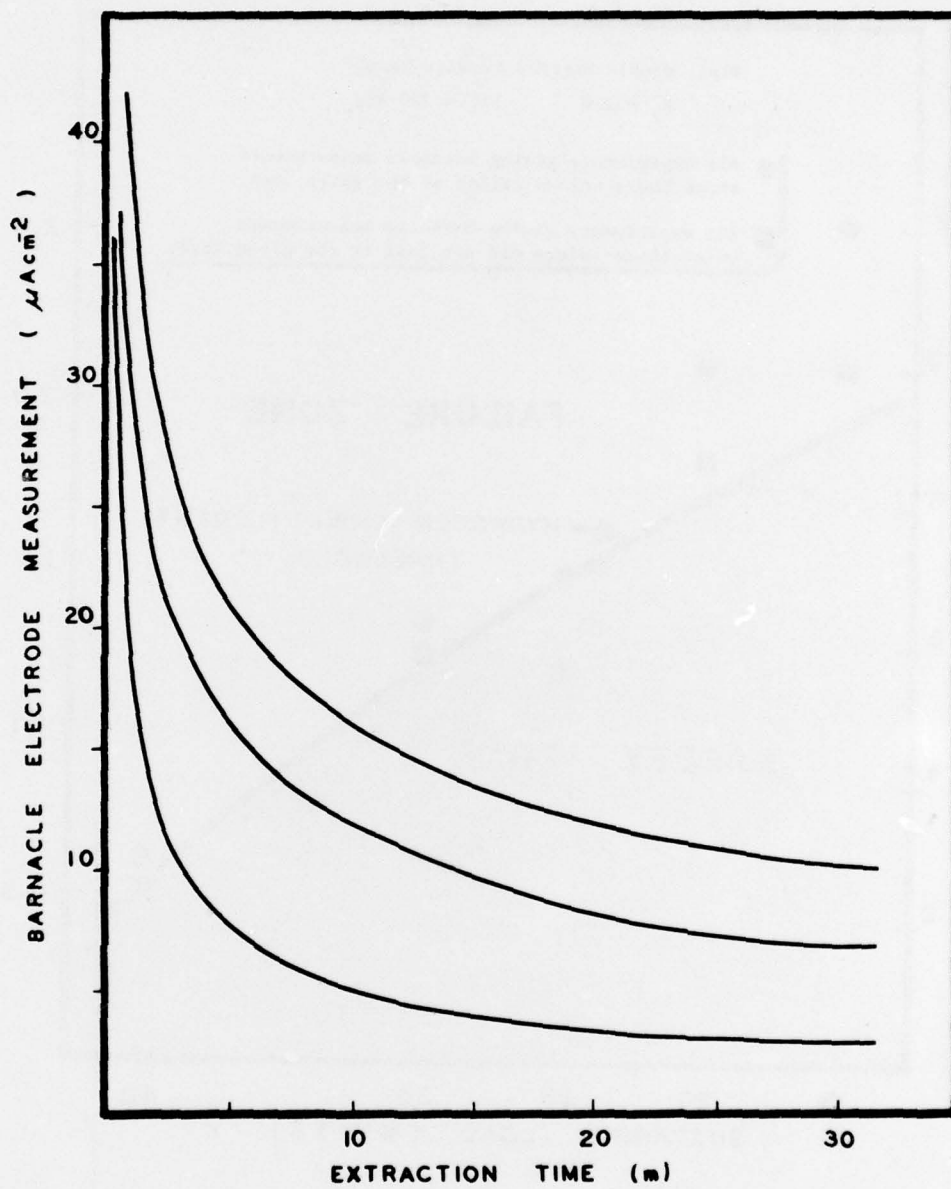


Figure 3. Typical Barnacle Electrode Hydrogen Extraction Transients

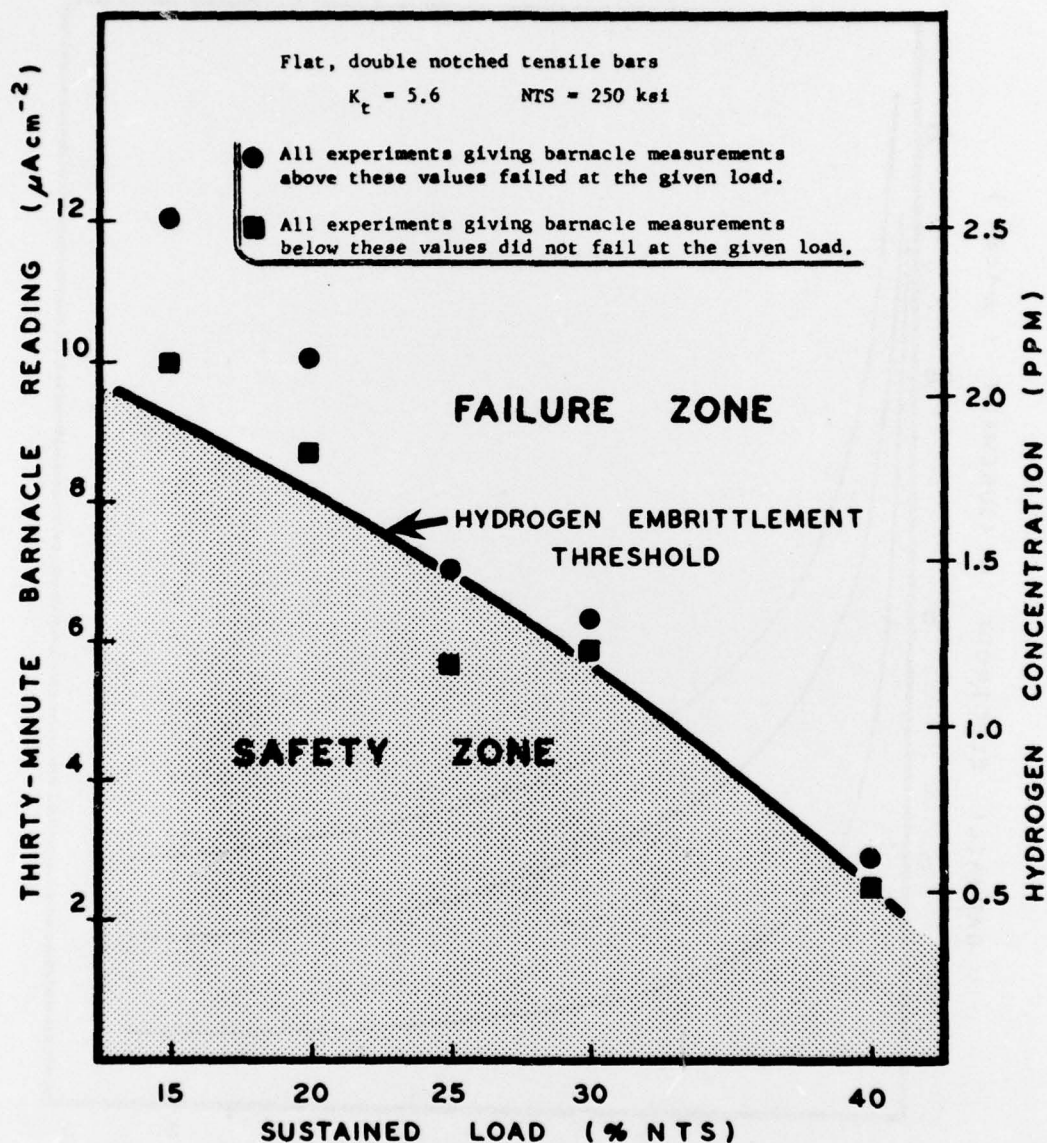


Figure 4. Indexing the Degree of Hydrogen Embrittlement of AISI 4340 Steel Using Thirty-Minute Barnacle Electrode Measurements.

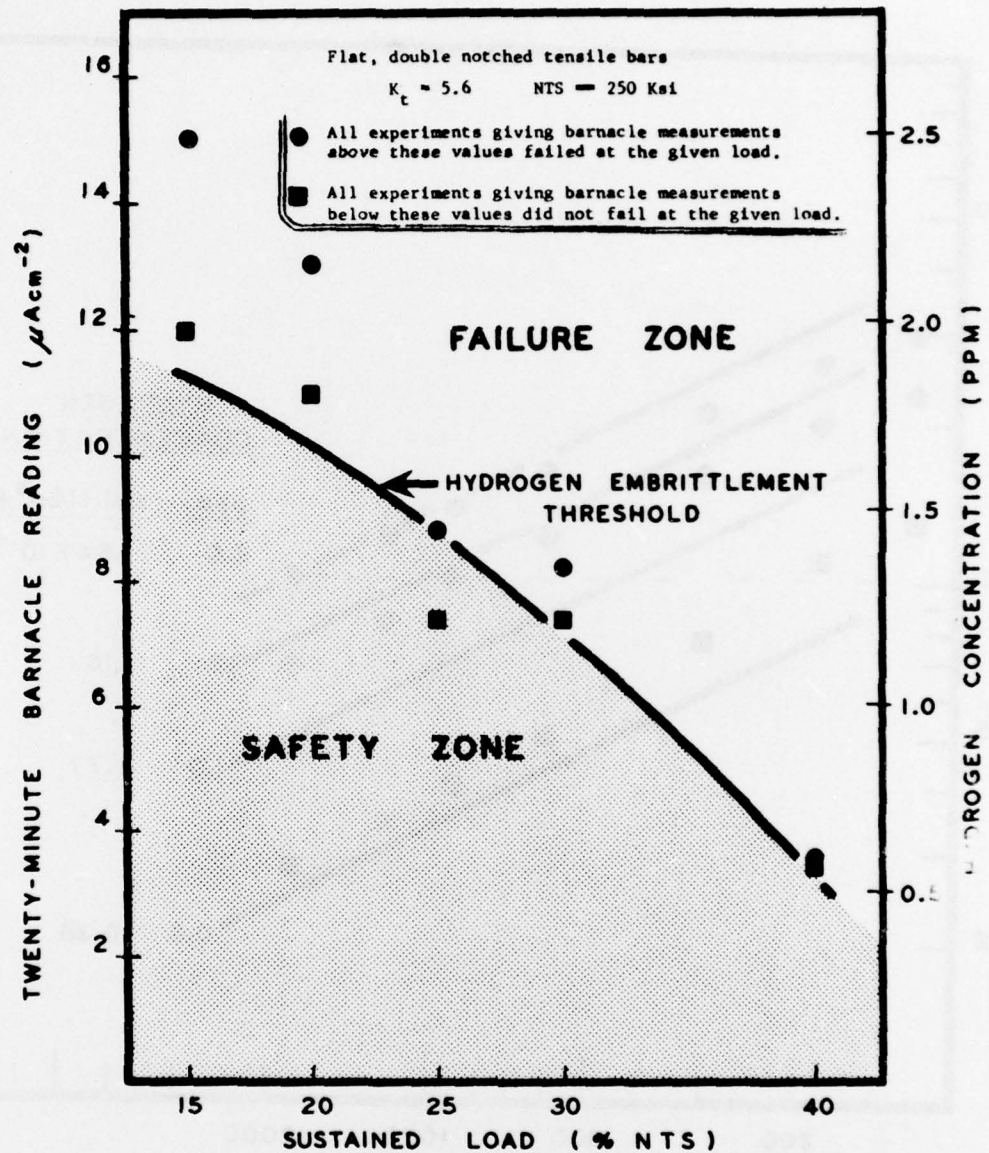


Figure 5. Indexing the Degree of Hydrogen Embrittlement of AISI 4340 Steel Using Twenty-Minute Barnacle Electrode Measurements.

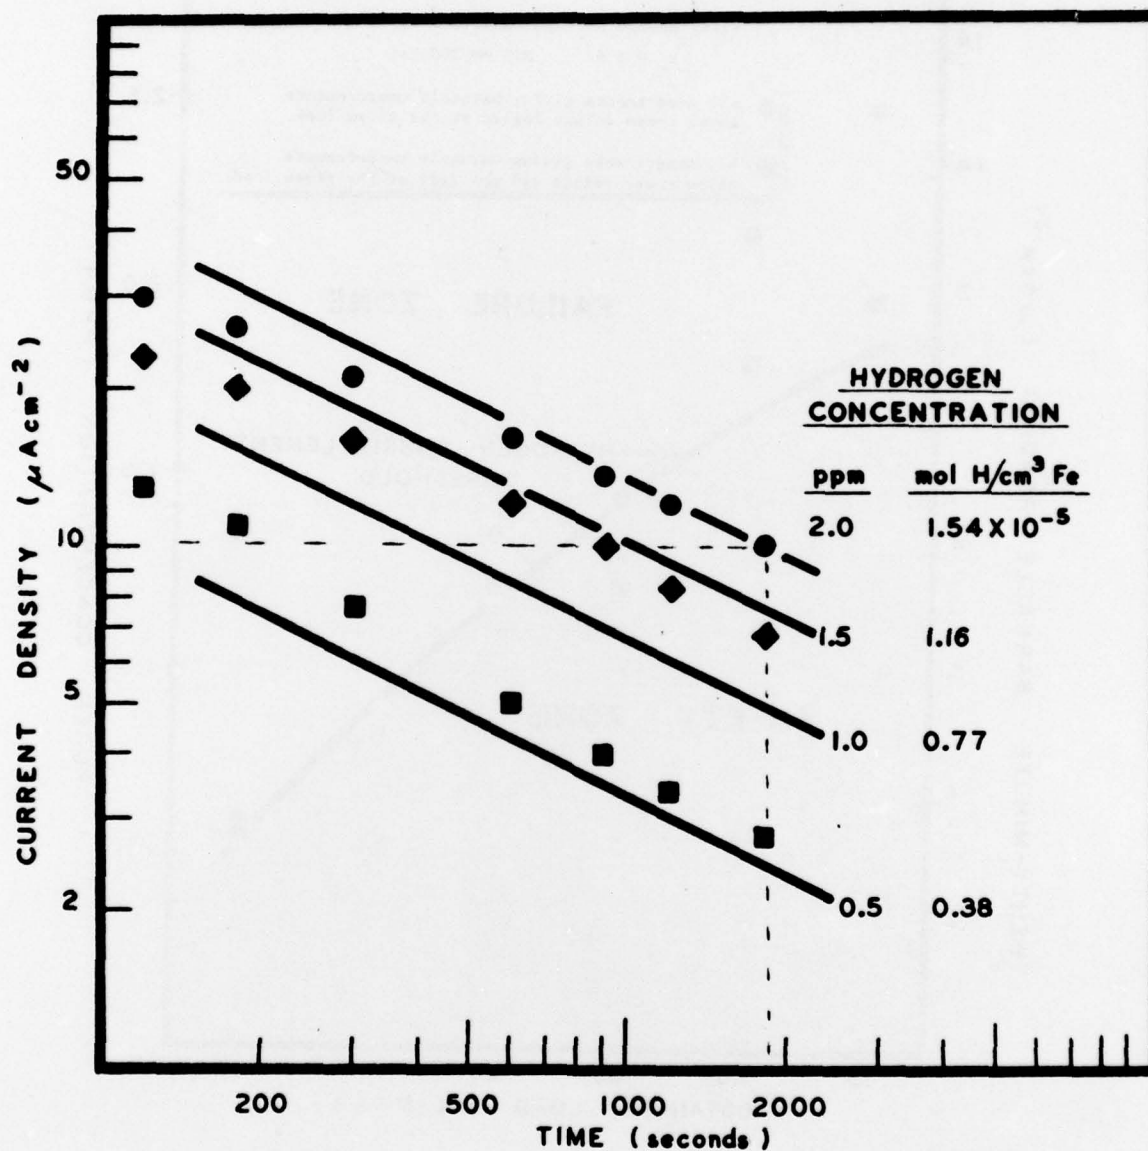


Figure 6. Barnacle Electrode Hydrogen Extraction Transients vs Theoretical Curves Calculated from Equation (1) for AISI 4340 Steel,  $D = 2.5 \times 10^{-7} \text{ cm}^2\text{s}^{-1}$ .



can be used in conjunction with a barnacle reading to determine the mobile hydrogen concentrations. Taking a 30-minute barnacle reading of  $10 \mu\text{A}/\text{cm}^2$ , for example, it is seen by the dotted lines in Figure 6 that the hydrogen concentration is  $1.5 \times 10^{-5} \text{ mol}/\text{cm}^3$  (2.0 ppm).

Alternatively, hydrogen concentrations can be calculated using Equation (1). Table II shows the results of these calculations for all of the specimens used in this study at selected extraction times. Concentrations are given in parts per million ( $1 \text{ mol H}/\text{cm}^3 = 1.3 \times 10^5 \text{ ppm}$ ). It can be seen that the calculated concentrations agree for each specimen from 15 to 30 minutes indicating agreement with the theoretical equation.

TABLE II

Calculated Hydrogen Concentrations (ppm) from Barnacle Electrode Measurements at Selected Extraction Times.

Specimen No.	5	10	15	20	30 min.
1	1.1	1.5	1.0	1.0	.99
2	1.6	2.3	1.7	1.6	1.6
3	1.6	2.5	1.7	1.8	1.7
4	1.7	2.7	1.9	2.0	2.0
5	---	3.5	2.4	2.5	2.4
6	1.7	2.5	1.9	1.8	1.8
7	1.9	2.8	2.0	2.1	2.0
8	.63	.85	.57	.56	.57
9	.99	1.5	1.0	1.0	1.1
10	1.2	1.8	1.3	1.2	1.2
11	1.4	2.0	1.4	1.5	1.4
12	1.2	1.8	1.4	1.5	1.5
13	1.4	2.0	1.3	1.2	1.2
14	1.3	2.0	1.4	1.4	1.4
15	1.5	2.2	1.4	1.4	1.3
16	.77	.95	.61	.56	.51
17	.58	.82	.57	.58	.59
18	.99	1.6	1.1	1.1	1.0
19	.52	.65	.44	.43	.45



### C O N C L U S I O N S

This study confirmed preliminary results that the barnacle electrode could be used to index the degree of hydrogen embrittlement of a high strength steel, and that reproducible results, which fit the theoretical equation, could be obtained. By using flat, double notched tensile specimens of AISI 4340 steel having a notched tensile strength of 250 ksi (1725 MPa) and a  $K_t$  of 5.6, critical hydrogen concentrations for failure of 1.9, 1.7, 1.4, 1.2, 0.9 and 0.5 ppm were found for sustained loads of 15, 20, 25, 30, 35 and 40 percent of the NTS, respectively. It was shown that hydrogen concentrations as low as 0.5 ppm can be determined, and that these low levels of hydrogen can be embrittling. It was further shown that twenty-minute measurements are as suitable as those taken at thirty minutes.

### A C K N O W L E D G E M E N T S

The author wishes to thank Dr. J. J. DeLuccia, Head of the Materials Protection Branch, and Mrs. S. J. Ketcham, Head, Corrosion Mechanisms and Control Section, for their encouragement and suggestions.

R E F E R E N C E S

- (a) A. R. Troiano, Trans. ASM, Vol. 52, 54 (1960).
- (b) J. H. Shively, R. R. Hehemann and A. R. Troiano, Corrosion, Vol. 22, 253 (1966).
- (c) W. Beck, E. J. Jankowsky and P. Fischer, "Hydrogen Stress Cracking of High Strength Steel," Naval Air Development Center Report No. NADC-MA-7140, December 1971.
- (d) D. A. Berman, W. Beck and J. J. DeLuccia, "Hydrogen in Metals," I. M. Bernstein and A. W. Thompson (Eds.), American Society for Metals (1974).
- (e) D. A. Berman, Naval Air Development Center Report No. NADC-74219-30, December 1974.
- (f) M. A. V. Devanathan and Z. Stachurski, Proc. Roy. Soc., Vol. A270, 90 (1962).
- (g) M. A. V. Devanathan, Z. Stachurski and W. Beck, J. Electrochem. Soc., Vol. 110, 886 (1963).
- (h) E. Gileadi and M. Fullenwider, University of Pennsylvania Final Report to Naval Air Engineering Center, Contract No. N156-46659, September 1966.
- (i) W. Beck, A. L. Glass and E. Taylor, J. Electrochem. Soc., Vol. 112, 53 (1965).
- (j) M. Genshaw and P. K. Subramanyan, University of Pennsylvania First Quarterly Report to Naval Air Engineering Center, Contract No. N00156-67-C-1941, June 1967.

NADC-76359-30

This page intentionally blank

D I S T R I B U T I O N   L I S T

Dr. Kevin Kondas (Code 6101)  
Naval Ship Engineering Center  
Hyattsville, MD 20282

Milton Levy  
Army Materials & Mechanics Research  
Center  
Watertown, MA 02172

Dr. James R. Myers  
Dept. of Civil Engineering  
Air Force Institute of Technology  
Wright-Patterson Air Force Base  
Dayton, OH 45433

Phillip A. Parrish, Metallurgist  
Army Research Office  
Research Triangle Park, NC 27709

Kent R. Petersen, OO-ALC Manager  
U. S. Air Force Ogden ALC  
MMETP  
Hill AFB, UT 84406

S. G. Fishman  
Head, Metal Materials Branch  
Naval Surface Weapons Center, WR-32  
White Oak, MD 20910

Leonard Moskowitz  
Sup. Metallurgist (Code 915)  
Naval Air Engineering Center  
Lakehurst, NJ 08733

Dr. R. J. H. Wanhill  
National Aerospace Laboratory  
Amsterdam, The Netherlands

Al Hohman  
Vought Corporation  
P. O. Box 5907  
Dallas, TX

Dr. L. J. McEwen  
Republic Steel Corporation  
P. O. Box 700  
Canton, OH 44701

Prof. C. J. McMahon, Jr.  
University of Pennsylvania  
LRSM K1  
Philadelphia, PA 19174

Dr. W. F. Savage  
Rensselaer Polytechnic Institute  
Materials Engineering Dept.  
Troy, NY

Dr. A. W. Thompson  
Rockwell International Corp.  
Science Center  
Thousand Oaks, CA 91360

Dr. I. M. Bernstein  
Carnegie Mellon University  
Dept. of Met & Mat Science  
Pittsburgh, PA 15213

CONTINUED FROM BACK OF COVER



# D I S T R I B U T I O N   L I S T

REPORT NO. NADC-76359-30

AIRTASK NO. R 0220 101

Work Unit No. DG 202

	<u>No. of Copies</u>
NAVAIR (AIR 954). . . . .	6
2 for retention	
1 for AIR 320	
1 for AIR 5203	
1 for AIR 52031	
1 for AIR 52031C	
 NAVSHIPPRANDCEN, Annapolis (Codes 2821/2813) . . . . .	 2
NAVSEC, Washington, DC (SEC 6120D). . . . .	1
ONR, Washington (Code 471). . . . .	1
ONR, Boston (Dr. Frank Gardner) . . . . .	1
NRL, Washington, DC (Dr. E. Metzbowser (Code 6311)). . . . .	1
WPAFB, Ohio (AFML/LL, AFML/LA, AFML/MXA). . . . .	3
 U. S. Steel, Applied Research Laboratory. . . . .	 1
Monroeville, PA.	
(E. H. Phelps)	
 NAVAIRDEVCEEN, Warminster, PA. . . . .	 52
3 for 813	1 for 30P7
2 for 30023	1 for 301
1 for 03	1 for 302
1 for 20	35 for 3022
1 for 30	1 for 303
1 for 40	1 for 304
1 for 50	1 for 305
1 for 60	
 DDC . . . . .	 12

CONTINUED ON INSIDE OF COVER