

AD-A050 920

AMERICAN UNIV WASHINGTON D C
DEFINITION OF CHEMICAL AND ELECTROCHEMICAL PROPERTIES OF A FUEL--ETC(U)
FEB 78 T SARADA, J F MCINTYRE, R T FOLEY

DAAK70-77-C-0080

F/G 10/2


NL

UNCLASSIFIED

| OF |
AD
A050920



END
DATE
FILMED
4 - 78
DDC

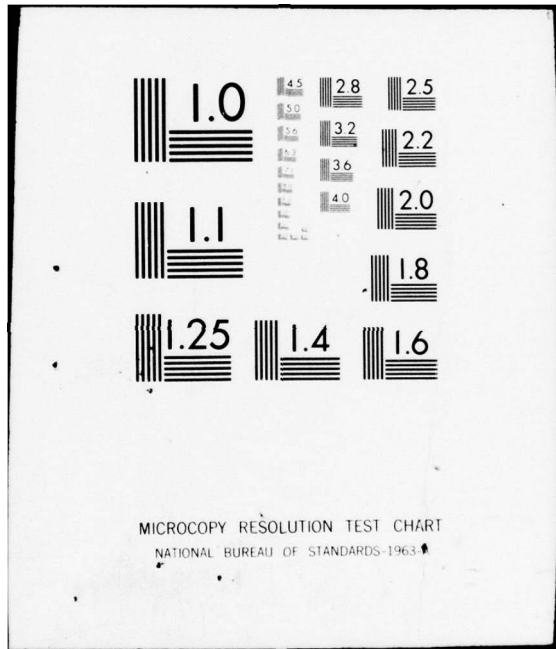


MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD A 050920

12

AD No. _____
MIC FILE COPY

RECEIVED
MAR 7 1978
F

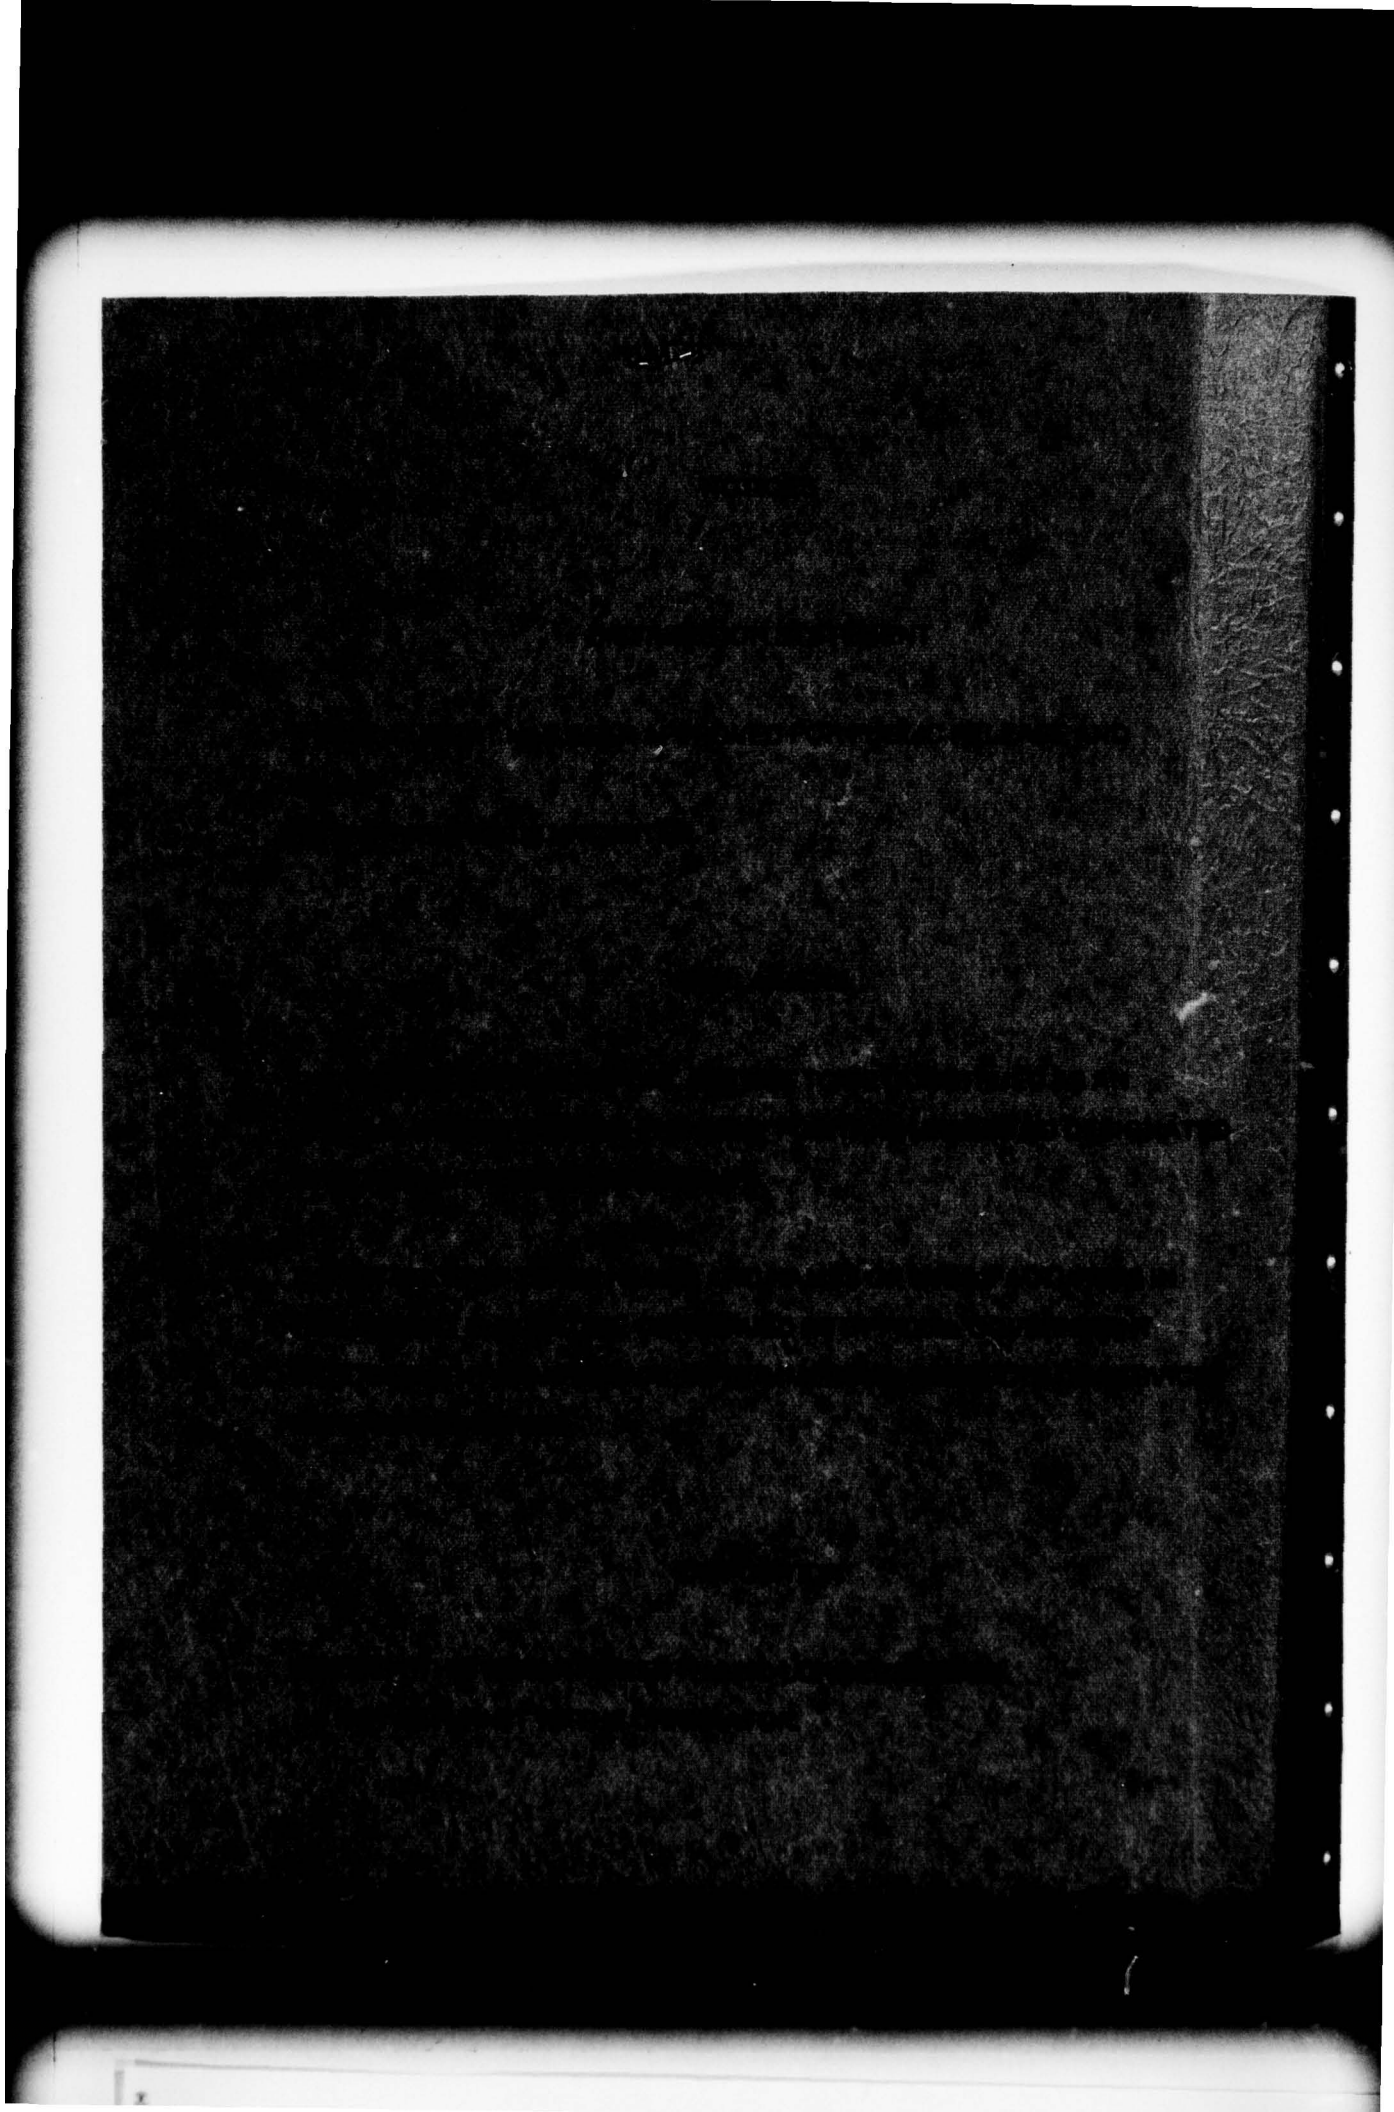

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

| REPORT DOCUMENTATION PAGE | | READ INSTRUCTIONS BEFORE COMPLETING FORM |
|--|-----------------------|---|
| 1. REPORT NUMBER | 2. GOVT ACCESSION NO. | 3. RECIPIENT'S CATALOG NUMBER 9 |
| 4. TITLE (and Subtitle) 6 Definition of Chemical and Electrochemical Properties of a Fuel Cell Electrolyte | | 5. TYPE OF REPORT & PERIOD COVERED Interim Technical Report, March 25, 1977-December 24, 1977 |
| 7. AUTHOR(s) Sarada, T., McIntyre, John F., and Foley, R.T. | | 6. PERFORMING ORG. REPORT NUMBER 25 Mar 77-24 Dec 77 8. CONTRACT OR GRANT NUMBER(s) 15 DAAK70-77-C-0080 |
| 9. PERFORMING ORGANIZATION NAME AND ADDRESS The American University Washington, D.C. 20016 | | 10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS IT161102A34A 16 100 EF |
| 11. CONTROLLING OFFICE NAME AND ADDRESS U.S. Army Mobility Equipment Research and Development Command, Fort Belvoir, Virginia | | 12. REPORT DATE 11 February 1978 |
| 14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 12 46p. | | 13. NUMBER OF PAGES 36 + iv |
| 16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited. 10 T. Sarada | | 15. SECURITY CLASS. (of this report) Unclassified |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in block 20, if different from Report) John F. McIntyre R. T. Foley | | 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE |
| 18. SUPPLEMENTARY NOTES | | |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Electrochemistry, Fuel cell, Electrolytes, Conductivity, Polarization | | |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The present research is oriented toward the task of developing an improved electrolyte for the hydrocarbon-air fuel cell. A literature study of the properties of organic acids indicated that the following typed of compounds warranted further investigation: 1. Aromatic poly carboxylic acids - partially neutralized | | |


D D C
RECEIVED
MAR 7 1978
REGISTERED
F

027650


JFB

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

- 
2. Perfluoroaliphatic carboxylic acids
 3. Mono, di and poly sulfonic acids.
 4. Substituted sulfonic acids

This was followed by an experimental program wherein the vapor pressure, wetting characteristics, electrical conductivity, chemical stability, and electrochemical stability were measured.



UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Unclassified

DEFINITION OF CHEMICAL AND ELECTROCHEMICAL PROPERTIES
OF A FUEL CELL ELECTROLYTE
Interim Technical Report

by

T. Sarada, John F. McIntyre and R. T. Foley

February 1978

to

U. S. Army Mobility Equipment Research and
Development Command
Fort Belvoir, Virginia

Prepared by

The American University
Washington, D.C.

Contract No. DAAK70-77-C-0080

DA Project/Task Area/Work Unit No. 1T161102A34A 03 100 EF

Approved for public release and sale

distribution unlimited

Unclassified

| | |
|---------------------------------|---|
| ACCESSION for | |
| NTIS | White Section <input checked="" type="checkbox"/> |
| DDC | Blue Section <input type="checkbox"/> |
| UNANNOUNCED | <input type="checkbox"/> |
| DISSEMINATION | |
| BY | |
| DISTRIBUTION AVAILABILITY CODES | |
| SPECIAL | |
| A | |

TABLE OF CONTENTS

| | PAGE |
|--|------|
| Summary | 1 |
| Foreword | 11 |
| List of Figures | 111 |
| List of Tables | iv |
| I. Orientation of Present Research to Overall Fuel Cell Program | 1 |
| II. Scope of the Present Research | 2 |
| III. Chemical and Physical Properties of Potential Electrolytes as Reported in the Literature | 3 |
| 1. Carboxylic Acids | 4 |
| 2. Substituted Carboxylic Acids | 6 |
| 3. Sulfonic Acids | 10 |
| 4. Substituted Aliphatic Sulfonic Acids | 11 |
| 5. Summary | 12 |
| IV. Chemical and Physical Properties of Potential Electrolytes - Experimental | 15 |
| Specific Conductance | 15 |
| Wetting | 19 |
| Chemical Stability | 19 |
| Electrochemical Behavior (voltage sweep experiments) | 21 |
| V. Conclusions and Directions of Future Work | 33 |
| VI. References | 35 |

SUMMARY

The present research is oriented toward the task of developing an improved electrolyte for the hydrocarbon-air fuel cell. A literature study of the properties of organic acids indicated that the following types of compounds warranted further investigation:

1. Aromatic poly carboxylic acids - partially neutralized.
2. Perfluoroaliphatic carboxylic acids.
3. Mono, di and poly sulfonic acids.
4. Substituted sulfonic acids.

This was followed by an experimental program wherein the vapor pressure, wetting characteristics, electrical conductivity, chemical stability, and electrochemical stability were measured.

FOREWARD

This research on the chemical and electrochemical properties of fuel cell electrolytes has been sponsored by the U. S. Army Mobility Equipment Research and Development Command at Fort Belvoir, Virginia, under Contract No. DAAK 70-77-C-0080 with the American University. The work was authorized under DA Project/Task/Work Unit No. 1T1611 02A34A 03 100 EF.

List of Figures

| | Page |
|---|------|
| Figure 1. Specific conductance of aqueous solutions of trifluoromethanesulfonic acid monohydrate at 40° and 80°C | 18 |
| Figure 2. Set up for the stability testing | 20 |
| Figure 3. A schematic of the isopiestic vapor pressure cell | 24 |
| Figure 4. Vapor pressure isotherms of phosphoric acid solutions plotted from the data given in reference 19 and 20 | 27 |
| Figure 5. Vapor pressure plots of phosphoric acid solutions versus inverse temperature data from references 19 and 20 | 28 |
| Figure 6. Cyclic voltammogram of dichloroacetic acid | 30 |
| Figure 7. Cyclic voltammogram of dl-10 camphorsulfonic acid | 31 |
| Figure 8. Cyclic voltammogram of heptafluorobutyric acid | 32 |

List of Tables

| | | Page |
|------------|--|------|
| Table I. | A Summary of the Available Data on Some Proposed Electrolytes | 13 |
| Table II. | Conductance Data for Solutions of Proposed Electrolytes | 16 |
| Table III. | Conductivity of Water Solutions of Trifluoromethanesulfonic Acid Monohydrate Solutions | 17 |
| Table IV. | Contact Angles of Electrolytes on Teflon at Room Temperature | 22 |
| Table V. | Summary of Preliminary Tests on Electrolytes | 23 |
| Table VI. | Results of Quantitative Hydrolysis Testing | 25 |
| Table VII. | Concentrations of Some Electrolytes, Isopiestic With About 85% H_3PO_4 at Room Temperature | 26 |

I. ORIENTATION OF PRESENT RESEARCH TO OVERALL FUEL CELL PROGRAM

The tremendous amount of technical work performed during the last two decades has demonstrated that the fuel cell is indeed a feasible energy conversion device. A recent study (1) has described in detail the impact on the national economy of commercial applications of fuel cell power plants. Some of the same factors that bear on the employment of fuel cells by electric utilities also are pertinent to U.S. Army applications of fuel cells to vehicle propulsion and auxiliary power units. These include fuel conservation leading to energy cost savings, as well as better control of noise and emission levels. Further, fuel cells are more amenable to sizing to meet load requirements. For example, unlike some of the other methods of energy conversion, fuel cell capacity need not be installed at the ultimate required load level but rather, can be added in steps. The employment of modules to meet gradually increased demands is described in the report cited above (1). It is generally accepted now that the fuel cell offers distinct advantages for energy conversion plants of any size.

While the research and development in the fuel cell field has demonstrated the feasibility of the fuel cell as an energy conversion device there are substantial technical problems that remain. These problems are related to cost and endurance. By cost we might take a figure of \$160 per kilowatt of installed powerplant manufacturing cost; for endurance, 20 years operation. Improvements must be made with respect to the present materials of construction and electrode materials such as binders and catalysts. It is obvious that directly related to the endurance of the fuel cell are the electrolyte and

the corrosion rates and electrode performance that the electrolyte generates.

To improve the relative position of the fuel cell as a power generating device, two main approaches are being taken; one, the improvement of electrode catalysts, the second, the improvement of the electrolyte. These are, of course, interdependent. A specific catalyst must function and endure in a specific electrolyte.

The present research is concerned with the second approach to the problem, electrolyte improvement, and the selection of new electrolytes with better chemical, physical, and electrochemical properties than those presently used.

II. SCOPE OF THE PRESENT RESEARCH

The properties of the desired fuel cell electrolyte have been described in detail in a previous report from this laboratory (2). Briefly, the following qualifications are required

- a) the electrolyte should be a good medium for the oxidation of the fuel
- b) the electrolyte should be a good ionic conductor
- c) the electrolyte should be a good solvent for active materials and for material transport
- d) the electrolyte should be chemically and electrochemically stable over the operating temperature range
- e) the electrolyte should possess proper vapor pressure and viscosity characteristics
- f) the electrolyte should not be corrosive to fuel cell electrode materials or cell container materials.

Based on these properties a search is underway for chemical compounds, inorganic and organic, that will possess these properties and yet not possess those properties associated with phosphoric acid that have been found to be detrimental to fuel cell operation or endurance.

Thus, the scope of the research includes identifying potential new fuel cell electrolytes and evaluating them with the following chemical or electrochemical tests

hydrolysis

thermal stability

tests for halide ion (for halo-substituted compounds)

test for decarboxylation (for carboxylic acids)

solubility

conductivity

vapor pressure

hydrate formation

wetting of Teflon

surface tension

viscosity

electrochemical stability

adsorption of H₂ and propane on Pt electrodes

electrooxidation of H₂ and propane

electroreduction of air.

III. CHEMICAL AND PHYSICAL PROPERTIES OF POTENTIAL ELECTROLYTES AS REPORTED IN THE LITERATURE

The initial survey concentrated on protonic organic acids.

The protonic restriction was based on the desirability of finding an

electrolyte suitable for the hydrocarbon-air fuel cell, i.e., a CO_2 rejecting electrolyte. Also H^+ ions are required in the stoichiometry of the electrode reactions as well as providing solutions with high conductivity.

The literature search collected data on four classes of compounds

1. carboxylic acids--mono, di and poly, both aliphatic and aromatic
2. substituted carboxylic acids, particularly halo substituted aliphatic acids.
3. sulfonic acids--mono, di and poly, aliphatic, aromatic and bicyclic
4. substituted aliphatic sulfonic acids.

1. Carboxylic Acids

Aliphatic carboxylic acids (3,4,5)

In the saturated mono carboxylic acid the $-\text{COOH}$ group is resistant to reduction. But the β -position of a fatty acid is the primary point of attack in a reaction. The acid is not oxidized by air at ordinary temperatures but is by oxygen at elevated temperatures, especially in the presence of catalysts. KMnO_4 can degrade the carboxylic acid to give quite heterogeneous products. Also biological oxidative degradation involves the β -position. H_2O_2 attacks the acid, e.g., a 3% H_2O_2 solution oxidizes butyric acid to β -hydroxy butyric acid and then to acetoacetic acid and finally to acetone. The $-\text{COOH}$ group is relatively unstable at high temperatures and decarboxylation is a predominant reaction in the higher temperature range, in the presence of catalysts yielding ketones. Lower acids yield ketones,

olefines and cyclic hydrocarbons at 600°C; the presence of catalysts greatly lowering the temperature at which the fatty acid undergoes decomposition.

The carboxylate ion of the aliphatic acid is anodically oxidized at the Pt electrode at a very high positive potential, i.e., at +2.3 volts. The mono carboxylic acid has a very low solubility, low conductivity and high pK_a value.

The unsaturated mono carboxylic acid is a reducing agent and is generally not stable.

In view of this stability, aliphatic carboxylic acids, saturated and unsaturated, are not considered as promising electrolytes at this stage.

Di and poly-acids. The first effect of introducing a second carboxyl group is the decrease in the stability of the dicarboxylate anion. Formation of anhydride by loss of water, and decarboxylation usually result. The lower members decarboxylate quickly and the higher members form lactones, or anhydrides. pK_a values are low enough but supporting electrolytes may still be needed. Under a variety of pyrolytic conditions, fatty acids and their derivatives may suffer simultaneous or successive decarboxylation and dehydrogenation to unsaturated hydrocarbons. In a number of instances aromatic hydrocarbons or ketones are formed. Except in the presence of catalysts these are relatively resistant to the action of H_2O_2 . When oxidation occurs, it is not specific or directed and a wide variety of products from partial oxidation have been identified such as aldehydes,

hydroxy acids, ketones, hydrocarbons as well as CO_2 . In a buffered oxidation system the acid is always oxidized to CO_2 .

In view of their instability, we are not considering di or poly carboxylic acids as promising electrolytes.

Aromatic carboxylic acids (3,4,5,6)


These are not strong acids (pK_a values are typically in the range of 4-5 at 25°C). The dicarboxylic acids are sparingly soluble in water. The tricarboxylic, the asymmetric ones, like trimellitic acid have reasonably high acid strengths although the solubility is rather low, i.e., less than 10 grams in 100 ml. With neutralization of one or two of the carboxyl groups a good protonic solvent may result. Trimellitic acid is being given further consideration.

2. Substituted Carboxylic Acids (3-8)

The halogen substituted carboxylic acids fall into two subclasses, those with chlorine, bromine and iodine substitution and those with fluorine substitution. Those with chlorine, bromine, and iodine substitution will be discussed first. These acids are stronger than the corresponding unsubstituted acids. But the kind and position of the halogen atoms in the alkyl chain affect the strength of the acid. A halogen in the α position increases the acidity far more than in the other positions. The effect seems to be electrostatic, the ionizable proton is in a region of relatively high positive charge because it is closer to the positive than the negative end of the larger C-X dipole. The ease of fission of the carbon-bromine bond in the 2-bromo alkanic acids appears to be related to the length of alkyl chain.

All of these halogen substituted acids are unstable to hydrolysis. With α -halo acids, substitution reactions predominate during hydrolysis; with β -halo acids, unsaturated acids are formed and with γ -acids lactones are formed. These reactions are accelerated by the presence of alkalis. The product, irrespective of the position of the halogen, is formed either by dehydrogenation or by substitution of new groups. This applies to di and poly halogen substitution as well.

In polarographic reduction according to the equation




the ease of reduction increases progressively as the homologous series is ascended from acetic to decanoic acid.

The ease of replacement of the halogen in fatty acids is in the same order as in alkyl halides, namely $\text{RI} > \text{RBr} > \text{RCI} > \text{RF}$. The bromo and chloro acids can be selectively reduced electrolytically under controlled conditions.

In view of the above reactions no compound was chosen from the chlorine, bromine, or iodine substituted carboxylic acid subclass.

Fluoro-containing carboxylic acids respond normally in many chemical reactions although the reaction rates are determined by the contribution of fluorine to the overall polarity in reactions involving ionic mechanisms. The CF_3 group, for example, is strongly electronegative and exerts a pronounced effect when it is not too remote from the carboxyl group.

Two illustrations are included here to show the unique characteristic bestowed on the carboxyl group by fluoro-substitution.

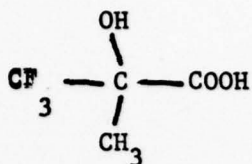

α -trifluoro methyl- α -hydroxy propionic acid

(trifluoro-lactic acid) shows an unusual reluctance to form a lactide whereas the unsubstituted acid dehydrates very easily.

Removal of F from C-F to form an olefin is much more difficult energetically than to remove H₂ from C-H. With partial fluorination the compounds become unstable.

β -fluoro acids resemble β -hydroxy acids in the ease in which unsaturates are formed. In β -difluoro acids this activity should be increased because of the additional inductive effect of the -CF₂- which makes the α -H more mobile.

Difluorosuccinic acid (CHF-COOH)₂ is extremely reactive even with water and immediately forms acetylinic dicarboxylic acids.

Some observations on specific members are pertinent in evaluating this subclass of compounds.

Trifluoroacetic acid hydrolyses rather easily.

Trifluoroacetic acid decomposes thermally, very likely, to give a difluorocarbene and CO₂.

Perfluoropropionic acid shows a tendency for hydrolysis.

In water, perfluorobutyric acid, C₃F₇COOH, slowly decarboxylates at 150°C. The aqueous solution of C₃F₇COOH has essentially the same pH as would be calculated for complete dissociation. The F atoms are stable toward hydrolysis. The compound withstands refluxing with dilute base for hours with negligible formation of fluoride ions.

Decarboxylation reactions are difficult with monocarboxylic acids.

See Table I for some data.

Perfluoroadipic acid. In the presence of $\text{Ba}(\text{OH})_2$ decarboxylation takes place at about 280°C .


One source (8) says that perfluoromalonic acid decarboxylates readily like malonic acid whereas another source (7) says that difluoromalonic acid, unlike malonic acid, is stable up to 160° .

The silver salts of mono and dicarboxylic acids react readily with halogens, Cl_2 , Br_2 and F_2 , around $80-100^\circ$ to give the respective halides.

The trifluoro methyl group in the β -position is hydrolysed at 100° in the presence of 2N NaOH, e.g. $\text{CF}_3-\underset{\text{CH}_3}{\text{CH}}-\text{COOH}$ to $\text{CH}_3\underset{(\text{COOH})_2}{\text{CH}}$

Unsaturated and aromatic perfluoro acids and derivatives are less stable.

The K and Na salts of perfluoroacids undergo thermal decomposition as follows:



Free perfluorocarboxylic acids lose HF and CO_2 and form a perfluoro-olefin when heated to a higher temperature.

Electrolysis of fluorinated alkyl acids in the presence of sodium methoxide gives fluorinated paraffins by coupling.

Perfluoroacetic acid is a good catalyst for polymerization and is a good condensing agent.

With respect to physical properties the effect of fluorine atoms on the acids is to increase the density, to decrease the refractive index, to lower the surface tension, and to increase the absolute viscosity.

Most of these fluoroacids form hydrates or compounds containing some definite hydrate or water-containing azeotropic mixture. The higher perfluoroacids in aqueous solutions are found to lower the surface tension of water to a larger extent than any other type of compound. The solubilities go down as we ascend the series; there is foaming and gel formations in aqueous solutions. From these observations it may be concluded that if any compound is to be chosen from this subclass the following guidelines should be used.

1. The maximum number of carbon atoms in the mono or dicarboxylic acid should be 4 or 5 and the minimum number 3.
2. The compound should be completely fluorinated and there should be no unsaturation or aromatic rings.

On the basis of the foregoing we have selected perfluorobutyric, C_3F_7COOH , perfluorosuccinic, $(CF_2COOH)_2$ and perfluoroadipic, $(CF_2)_4C_3F_7COOH$, acids for further study.

3. Sulfonic Acids (9, 10)

Aliphatic sulfonic acids

The lower members are strong electrolytes but from heptane upwards show a behavior similar to that observed with solutions of higher soaps, i.e., they form colloidal solutions.

RCH_2SO_3H : Boiling with dilute NaOH solution is without effect but heating in 5% NaOH solution above 300° under pressure results in slow decomposition.

The aliphatic sulfonic acids are, in general, inert towards the action of Cl_2 under ordinary circumstances.

Ethane sulfonic acid is stable towards chlorine but with solid alkalis reacts to give ethylene. The higher members, invariably, exhibit the properties of colloidal electrolytes.

Methionic acid or methanedisulfonic acid, $\text{CH}_2(\text{SO}_3\text{H})_2$, is a hygroscopic material which is strongly acidic in aqueous solutions. It forms a solid hydrate which separates from a concentrated solution of water. It is very stable to heat, acid, and alkali. No reaction takes place when heated with strong oxidizing agents such as nitric acid or chlorine. See Table I for other properties.

Aromatic sulfonic acids (9-10)


A basic characteristic of this class is ease of hydrolysis. Complete removal of water is essential for stabilization. Even the carboxyl substituted acids share this property. This applies to both compounds with the benzene ring as well as the naphthalene ring. Aromatic sulfonic acids, will be put to more thorough testing procedures before any decision is made.

4. Substituted Aliphatic Sulfonic Acids (9)

Compounds such as the fluorinated substituted aliphatic sulfonic acids, e.g., trifluoromethanesulfonic acid are being considered elsewhere and will not be discussed here.


The α -hydroxy acids undergo a variety of reactions. They decompose both in acid and alkali solutions giving the original carbonyl compounds.

A carboxyl substitution in the hydrocarbon chain increases the stability of the aliphatic sulfonic acid.



This is a hygroscopic solid which crystallizes as a monohydrate. It is very stable, unlike malonic acid, undergoing no decomposition when boiled with dilute acid or in alkaline solution. By heating to 190°C with conc. H_2SO_4 , CO_2 is evolved. With heat alone decomposition sets in at 245°C. Electrolytic oxidation gives CO_2 and H_2SO_4 . (This information is from a 1914 paper and it does not give the decomposition potential (21). See Table I for other physical data.

A bicyclic sulfonic acid 10-camphor (dl) acid is very soluble in water, stable and does not decompose readily according to the literature. See Table I for other physical properties of this compound.

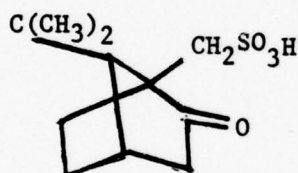

From a consideration of the literature bearing on the properties of the sulfonic acids, substituted and unsubstituted, it was decided that sulfoacetic acid, methionic acid, 1,2,3 propane sulfonic acid, and 10-camphor (dl) sulfonic acid will all be tested for suitability as fuel cell electrolytes.

5. Summary

Some of the pertinent data on those compounds of special interest are collected in table I. (11-14)

Table I. A Summary of The Available Data on Some Proposed Electrolytes.

| Compound Name and structure (pK_a , or k_a , where available) ^a | m.p./b.p. (°C) | Solubility and known reactivity | Specific conduct- ance ($\text{ohm}^{-1}\text{cm}^{-1}$, 40°C) (Measured here) |
|--|----------------------------------|---|--|
| 1. Trimellitic Acid (solid) (3.0×10^{-3} at 25°C) | 225-235° with decomposition | 5 gms in 100 ml. water at room temp- erature and increases to 8 gms or so at higher temperatures. An aq solution of potassium dihydrogen salt will be used as the electrolyte. | 0.112 for a 10% solution |
| 2. Heptafluorobuty- ric acid (liquid) $\text{C}_3\text{F}_7\text{COOH}$ $\text{C}_3\text{H}_7\text{COOH}$ ($k_a =$ 0.68) Relative acidity is the same as HNO_3 . | bp 120-121° | Miscible in water; slow decomposition at 150° in the pres- ence of water. Decar- boxylation at higher temperatures on heat- ing. | 44% solution 0.239. |
| 3. Sulfoacetic Acid $\text{CH}_2 - \text{COOH}$ SO_3H Very hygroscopic darkly colored solid. | mp of Mono- hydrate 84-86° | Very soluble in water. Very stable to heat. Decomposit- ion starts at 245°C. With conc H_2SO_4 , CO_2 is lost at 190°C. | 18% solution (as is) 0.3085. 58% solution 0.4640. |
| 4. Methane disulfonic acid (Methiononic acid) $\text{CH}_2 - \text{SO}_3\text{H}$ \diagdown SO_3H | bp 220° | Very soluble in water very hygroscopic; separates as a mono- hydrate from concentrated water solutions. Very stable to heat; slight decomposition at 160° C. Very stable to oxidizing agents like HNO_3 or Cl_2 . | |

Table I. continued

| | | | | |
|----|-----------------------------------|---|--|---|
| 5. | 10-Camphor- (dl) Sulfonic acid | Melts with decomposition at 193°C | Very soluble in water. Can be reduced with Na and alcohol. On fusion with KOH gives campholenic acid | 20% solution 0.2115 50% solution 0.293 |
|----|-----------------------------------|---|--|---|

IV. CHEMICAL AND PHYSICAL PROPERTIES OF POTENTIAL ELECTROLYTES-

EXPERIMENTAL

From the above literature review and other considerations, a number of compounds were selected for further study. These included the following:

sulfoacetic acid

trimellitic acid

dl-10 camphorsulfonic acid

methionic acid (methane disulfonic)

perfluorosuccinic or perfluoroadipic acid

1,2,3 - propane trisulfonic acid

heptafluorobutyric acid

These compounds were subjected to the following types of test:

specific conductance

wetting (contact angle on Teflon)

chemical stability

vapor pressure of solutions

electrochemical behavior (voltage sweep)

Specific conductance


The conductances of a number of solutions are given in table II; included is the conductance of phosphoric acid. In Table III, the conductances of solutions of trifluoromethane sulfonic acid monohydrate (TFMSA·MH) are given for comparison. These latter data at 40° and 80°C are plotted in figure 1. It is apparent that, with the exception of the chloroacetic acids, these solutions possess sufficient conductivity to make them interesting electrolytes.

Table II. Conductance Data for Solutions of Proposed Electrolytes

| <u>Compound</u> | <u>Concentration (weight percent)</u> | <u>Temperature</u> | <u>Specific conductivity (ohms⁻¹ cm⁻¹)</u> |
|--|---|--------------------|--|
| H ₃ PO ₄ | 85% | 40°C | 0.1381 |
| Dichloroacetic acid | 80% vol. | 40°C | 0.01883 |
| Trichloroacetic acid | 80 wt. % | 40°C | 0.01856 |
| Benzene Sulfonic acid | 5% | 40°C | 0.1217 |
| Sulfosalicylic acid | 5% | 40°C | 0.0767 |
| Sulfoacetic acid | 18% | 40°C | 0.3089 |
| | 58 | 39.8 | 0.4640 |
| Heptafluorobutyric acid | 43.59 | 40°C | 0.2388 |
| Trimellitic acid monopotassium salt | 10 | 40°C | 0.1124 |
| d1-10 camphorsulfonic acid | 20.81 (49.3 gm/100ml) | 40°C 40°C | 0.2149 0.2920 |

Table III. Conductivity of Water solutions of Trifluoromethane Sulfonic Acid Monohydrate Solutions

| Concentration (weight percent) | 40°C | specific |
|-----------------------------------|---------|--|
| | | conductance (ohms ⁻¹ cm ⁻¹) 80°C |
| 100 | 0.01122 | 0.0305 |
| 90 | 0.07109 | 0.1302 |
| 80 | 0.1847 | 0.3089 |
| 70 | 0.3232 | 0.5122 |
| 60 | 0.4309 | 0.7687 |
| 50 | 0.5500 | 0.8082 |
| 40 | 0.5750 | 0.8109 |
| 30 | 0.5400 | 0.7774 |
| 20 | 0.3802 | 0.5578 |
| 10 | 0.2391 | 0.3161 |

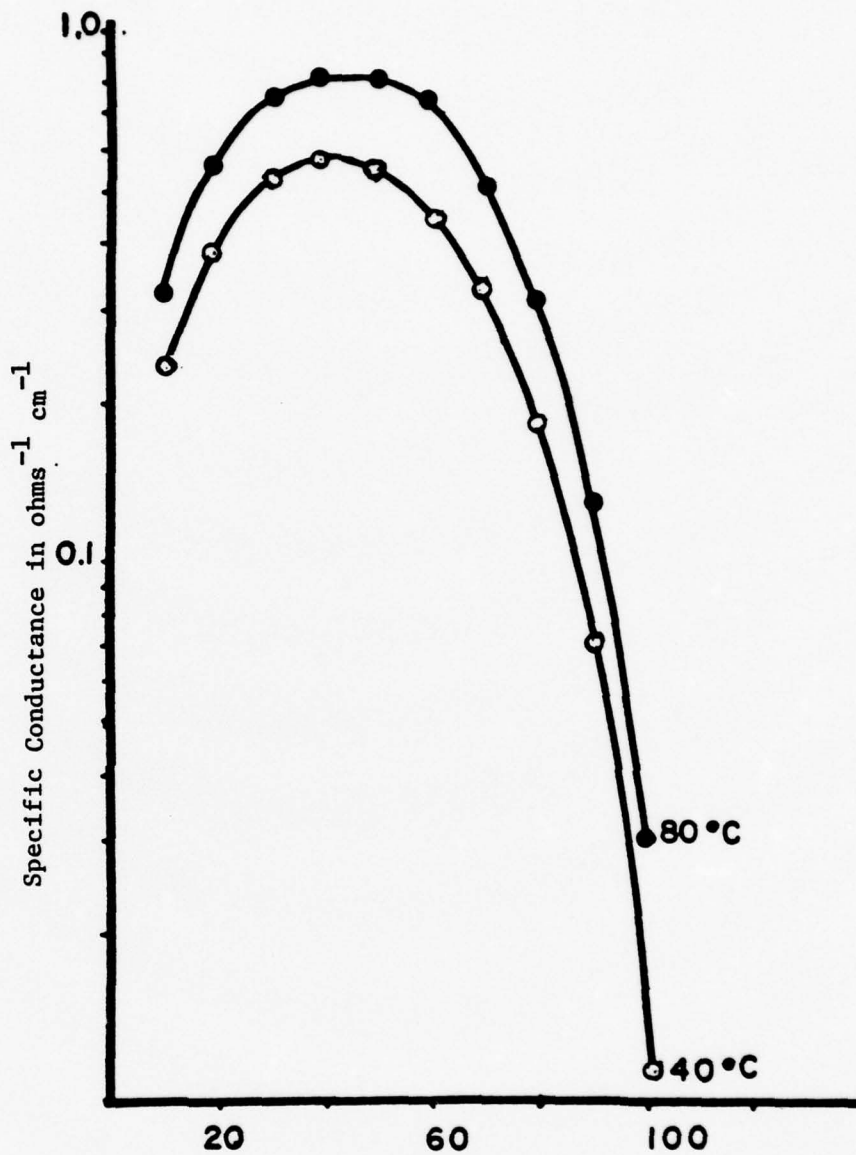

Weight percent concentration of aqueous TFMSA-MH.

Figure 1. Specific conductance of aqueous solutions of trifluoromethanesulfonic acid at 40° and 80°C.

Wetting (contact angle on Teflon)

The contact angle on Teflon was measured with a procedure described in a previous report (15). The results are given in Table IV. Those solutions with a contact angle of greater than 90° are considered to be non-wetting to Teflon.

Chemical Stability

The aqueous solutions of the acids were tested qualitatively for decomposition products. They were then refluxed and, while refluxing, argon gas was passed through the solution. The argon passed then through a train consisting of silica gel to pick up water and pre-treated barium hydroxide to pick up CO_2 , SO_2 , or HF. The changes in weight in the absorption tubes were determined. The acidities of the solutions, before and after refluxing, were determined volumetrically. The results of certain preliminary tests are given in table V and the results of some quantitative hydrolysis tests in Table VI. Solutions of sulfoacetic acid and dl-10 camphor sulfonic acid appear to be chemically stable to hydrolysis. On the other hand the aromatic sulfonic acids appear to be very susceptible to hydrolysis. This reaction must be confirmed because it could lead to the discarding of a whole class of electrolytes. The set up for the stability testing is shown in figure 2.

Vapor pressure of solutions

The vapor pressures of selected electrolyte solutions were measured by the isopiestic method (16-18). The method consists of equilibrating solutions of known and unknown vapor pressures in an isolated chamber for an extended period of time, during which period a good thermal contact is established between the pair. After equilibration the vapor pressures of the two solutions are the same and the respective concentrations

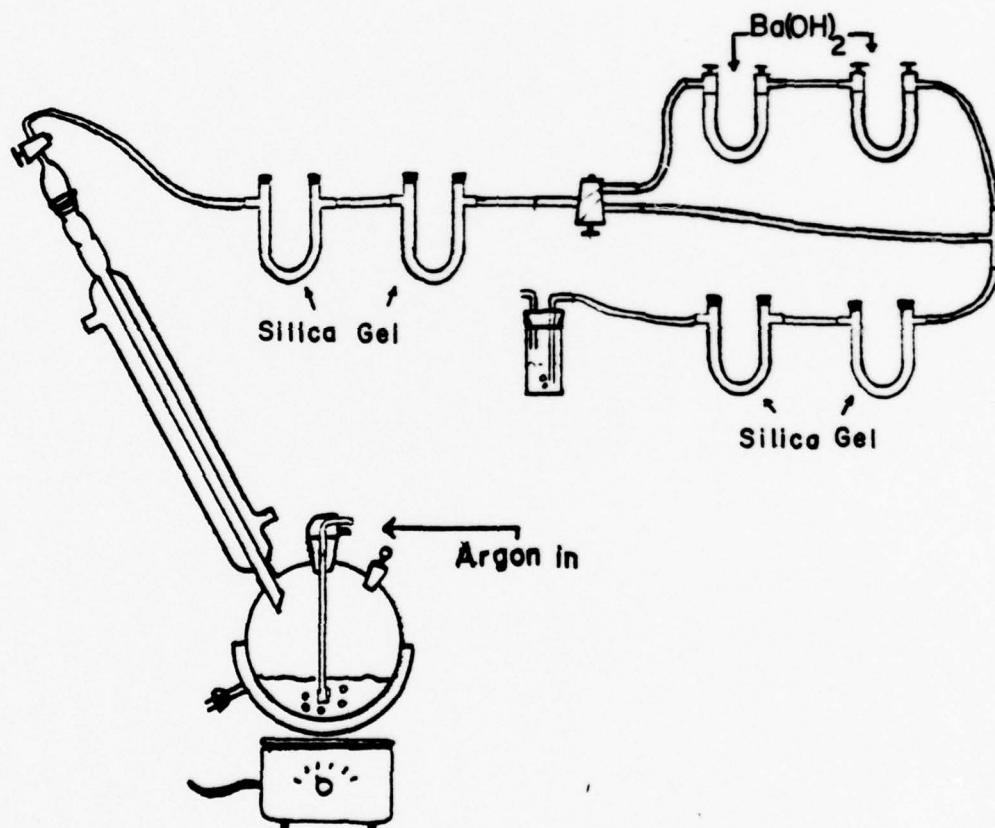


Figure 2. Set up for the Stability Testing

are measured. A chamber to permit such a thermal contact between two pairs of pyrex containers with a provision to close and open the individual containers without opening the chamber was designed and fabricated. This chamber is schematically shown in figure 3. The chamber was set inside a thermostated air oven during the experiment which lasted from 24 hours to a week. One of the drawbacks to the method is that the concentrations of the solutions cannot be prechosen, i.e., at a specific temperature the concentration of the unknown solution is adjusted so that the vapor pressure of this unknown solution is equal to the vapor pressure of the reference solution. Thus, the method requires knowing accurately the vapor pressure of a reference solution. In this investigation phosphoric acid solutions were used as references as the vapor pressure data over a wide range of temperatures are available. These data are compiled in a vapor pressure-composition plot in figure 4 which gives a series of isotherms. In figure 5 the vapor pressure is plotted versus the inverse temperature. The data for the unknown solutions were interpreted with these curves.

Table VII presents some electrolytes at concentrations isopiestic with approximately 85% phosphoric acid at room temperature.

Electrochemical behavior (voltage sweep experiments)

The experimental set up and the electrochemical cell were similar to that previously described (15). The following changes were made in these studies.

(1) A saturator was introduced into the argon bubbling system to compensate for water loss in aqueous solutions whenever they were used as electrolytes.

Table IV. Contact Angles of Electrolytes on Teflon at
Room Temperature. ($26^{\circ} \pm 1^{\circ}\text{C}$)

| <u>Solution</u> | <u>Concentration weight percent</u> | <u>Contact angle on Teflon</u> |
|--|---|------------------------------------|
| TMISA · monohydrate | 100 | 72.83 ^o |
| Methane sulfonic acid | 100 | 93.59 ^o |
| Trimellitic acid monopotassium salt | 10 | 97.59 ^o |
| dl-10 Camphor sulfonic acid | 50 | 81.06 ^o |
| Sulfoacetic acid | 59 | 90.15 ^o |

Table V. Summary of Preliminary Tests on Electrolytes

| Acid | Nature of test | Remarks |
|--|---|--|
| Dichloroacetic acid | Hydrolysis test | Very unstable in the presence of water. |
| Trichloroacetic acid | " | " |
| Dibromosuccinic acid | " | " |
| Heptafluorobutyric acid | Vapor pressure (see Table VII) | Very volatile. |
| Perfluorooctanoic acid | Solubility | Very soapy solution (froths and foams) |
| 2-3 naphthalene dicarboxylic acid | Solubility | Very low solubility. |
| Trimellitic acid | Solubility | Sparingly soluble and hence a monopotassium acid salt will be tested. |
| 5, Sulfosalicylic acid | An aqueous solution was tested with solution BaCl_2 | All the aromatic sulfonic acids give a precipitate on standing at room temperature and more easily on heating. |
| 1,5 naphthalene disulfonic acid | " | " |
| 1,3,6 naphthalene trisulfonic acid | " | " |
| Benzene sulfonic acid | " | " |
| Meta carboxylic benzene sulfonic acid | " | " |

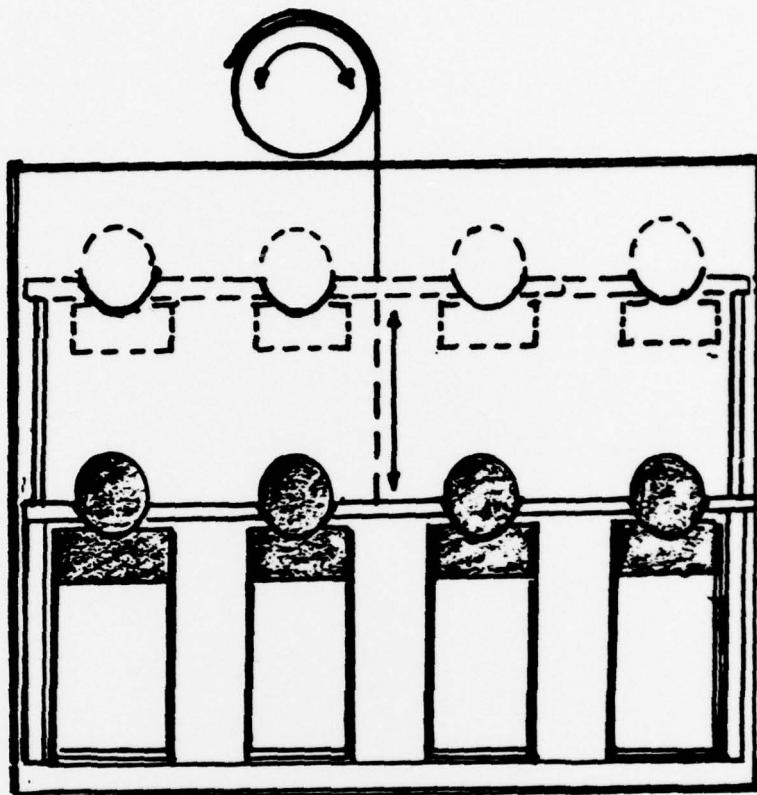


Figure 3. A schematic of the isopiestic vapor pressure cell.

Table VI. Results of Quantitative Hydrolysis Testing

| Acid Solution | Volumetric Analysis Strength | | Increase in Weight of Ba(OH) ₂ Tubes |
|---|------------------------------|---------|---|
| | Before | After* | |
| Sulfoacetic acid (approximately 59 gms in 100 ml) | 0.368N | 0.372N | 2.96 mgs. (a)** 17 mgs. (b) |
| Trifluoromethane sulfonic acid monohydrate (≈ 42 gms in 100 ml) | 0.2133N | 0.2096N | 18.7 mg (a) 13.5 mg (b) |
| 10-dl Camphor sulfonic acid (≈ 50 g in 100 g) | 0.1041 | 0.1062 | 30.5 mg (a) 26.8 mg (b) |

* Water loss was compensated before estimation. Since the volume compensation was approximate these solutions may be considered as stable to hydrolysis.

** (a) indicates initial experiment, (b) a similar experiment conducted 24 hours later.


Table VII. Concentrations of Some Electrolytes,
Isopiestic With About 85% H_3PO_4 at Room Temperature

| Electrolyte | Initial Concentration (weight percent) | Final Concentration | | | |
|-------------------------------------|--|---------------------------------------|-------------------------------------|-------------------------------------|-------------------------------------|
| | | (1) $t=24.5^{\circ}C$ ± 0.5 | (2) $25.5^{\circ}C$ ± 0.5 | (3) $26.5^{\circ}C$ ± 0.5 | (4) $26.5^{\circ}C$ ± 0.5 |
| Phosphoric acid | 85 | 79.6 (5.5mm)* | 82.28 (4.5) | 83.10 (4.5) | 80.17 (5.35) |
| TMMSA- Monohydrate | 100 | -- | 91.98 | 95.43 | 86.71 |
| Perfluoro butyric acid** | 100 | weight loss 4.44 | 4.53 | 4.67 | -- |
| Methane disulfonic acid | 50 | 52.05 | 51.30 | 51.10 | 54.25 |
| 10-Camphor (dl) sulfonic acid | 50.6 | 56.62 | 55.82 | 54.67 | 67.26 |
| Ethane 1-2 disulfonic acid | 50.85 | 52.73 | -- | 52.91 | 58.28 |
| Perfluoro succinic acid | 50 | 50.03 | 53.64 | 53.36 | 62.27 |
| Octafluoro adipic acid | 50 | 57.57 | 55.31 | 54.30 | 63.84*** |

* values of vapor pressure in mm of Hg given in parenthesis under concentration of H_3PO_4 . From references (19,20)

** very volatile liquid

*** this may be the limit of solubility at this temperature.

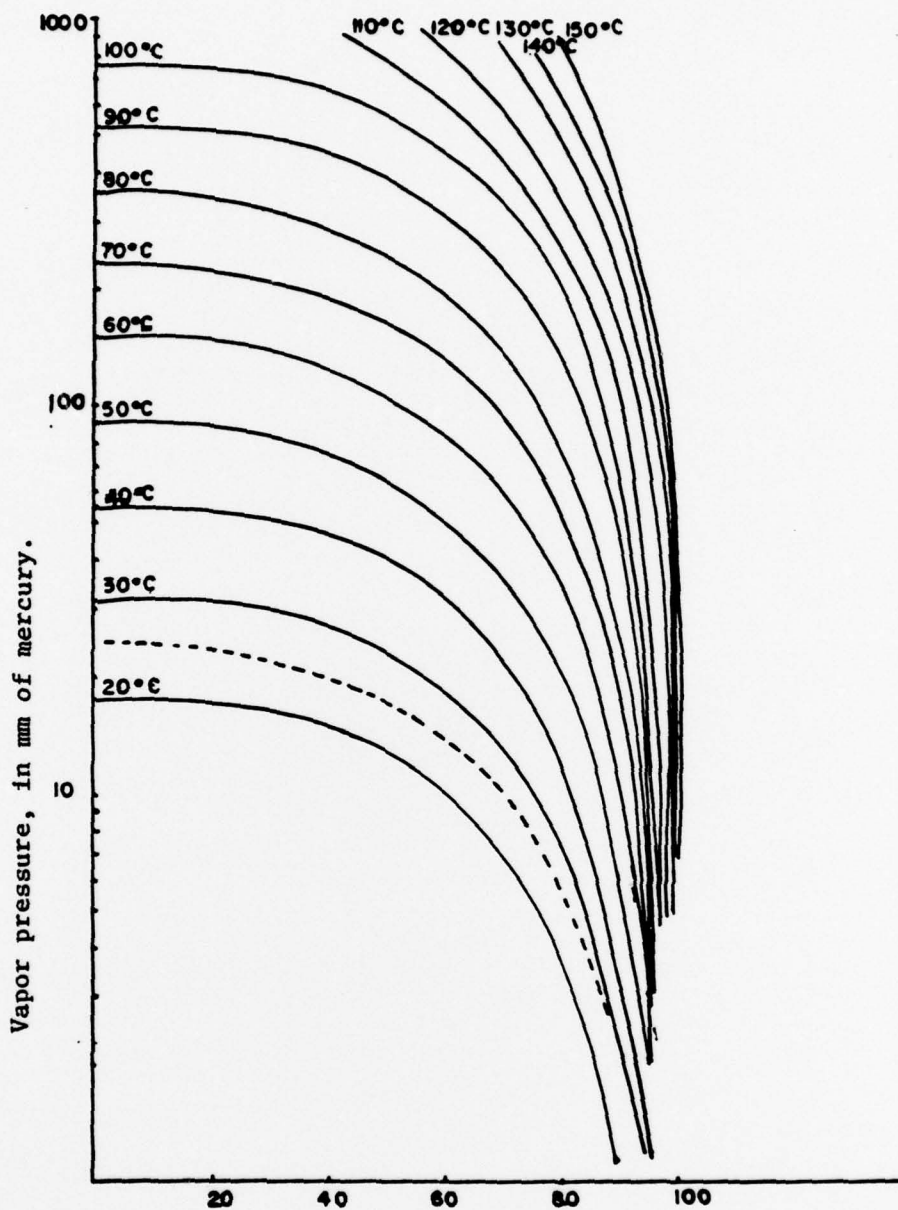

Weight percent concentration of aqueous phosphoric acid solutions.

Figure 4. Vapor pressure isotherms of phosphoric acid solutions plotted from the data given in references 19 and 20.

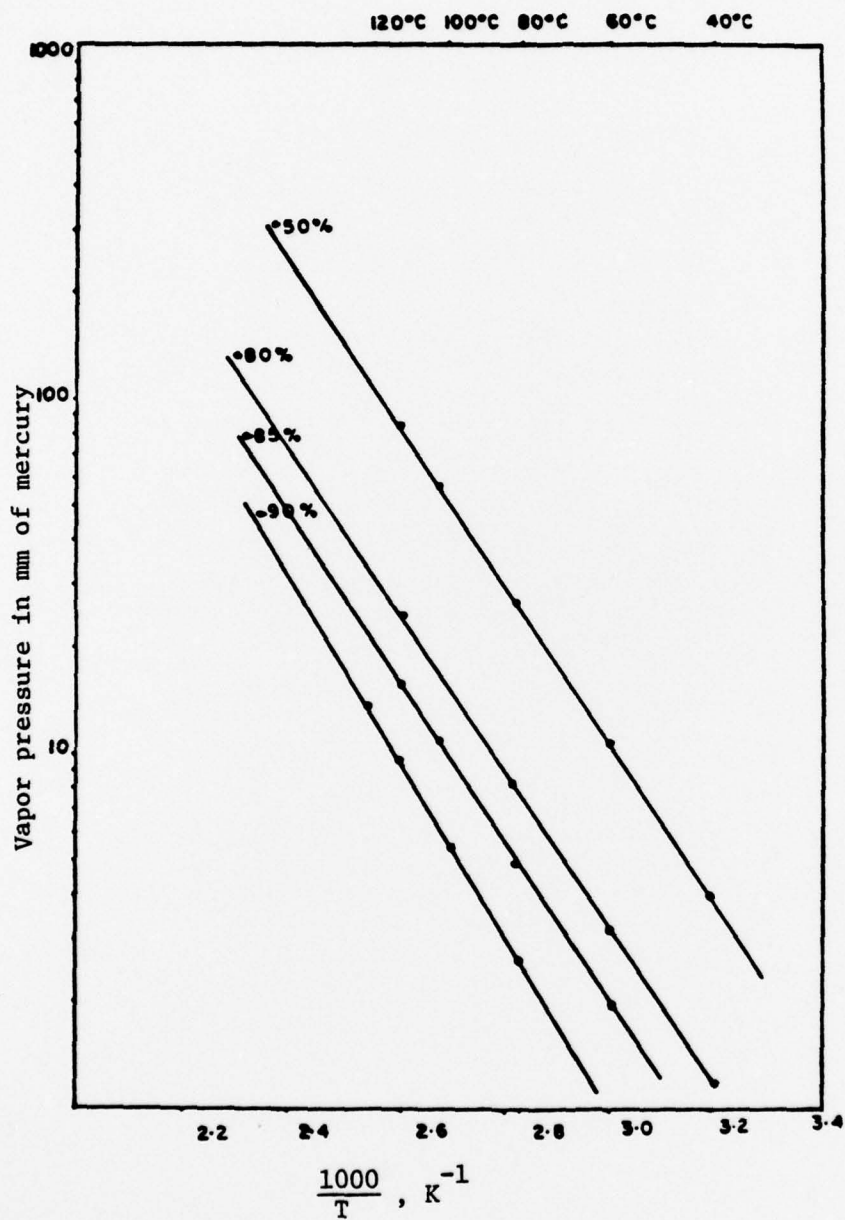


Figure 5. Vapor pressure plots of phosphoric acid solutions versus inverse temperature data from references 19 and 20.

(2) A lower temperature was used for the preliminary work reported here.

(3) Purging with argon was continued for a longer period of time before the start of the scan, but was stopped during the voltage scan to leave the system undisturbed.


(4) A new platinum electrode was used.

(5) The rate of sweep was reduced and a shorter voltage range was used.

The cyclic scan for dichloroacetic acid is given in figure 6. The solution was a 50% by volume solution with H₂O. The rest potential was 310 mV (versus DHE) and the scan rate was 50mV/sec.

Sweeping in the anodic direction a very low current was observed until about 600mV, then the current began to increase in the negative direction. The current changed from 0 μ A to -20 μ A between the anodic potentials 600 mV and 1200 mV. The scan direction was reversed at 1500 mV. Then the current decreased steadily from -40 μ A to -6 μ A as the potential decreased by 500 mV. A slight increase in current occurred and a cathodic reduction peak was found at 375 mV with a maximum current of 8 μ A. This peak is likely due to platinum oxide reduction. The dichloroacetic acid used in this experiment was vacuum distilled at 6mm from Fisher Scientific, purified grade. This electrolyte and other halogenated acids were found to be easily hydrolyzed in aqueous solution.


The voltage scan obtained with a solution 31% by weight of dl-10 camphor sulfonic acid is given in figure 7. This run was made at 80°C at a scan rate of 10 mV/sec. The rest potential was 360 mV. Preliminary to these experiments the system was purged for two hours with argon.

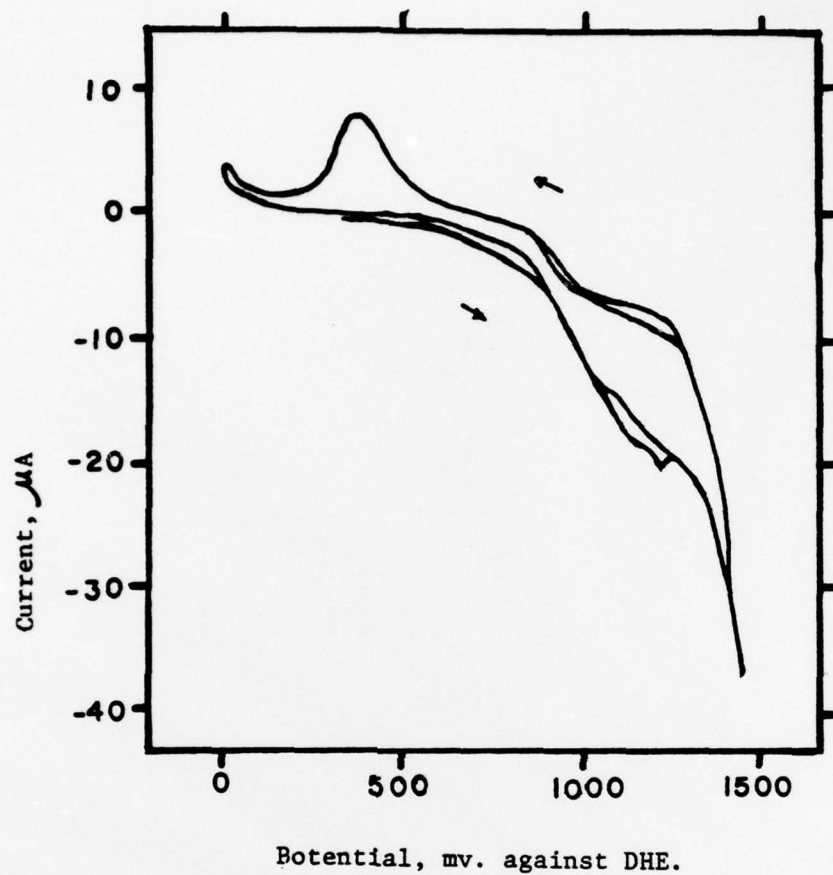

Dichloroacetic acid

| | |
|--------------------|----------------------|
| Concentration | 50% Volume |
| Bubbler | Yes |
| Temperature | 80°C |
| Rest potential | 310 mV (Pt. vs. DHE) |
| Scan rate | 50mV/sec |
| Voltage range | 0 to 1.5 V |
| Quiescent solution | No |


Figure 6. Cyclic voltammogram of dichloroacetic acid.

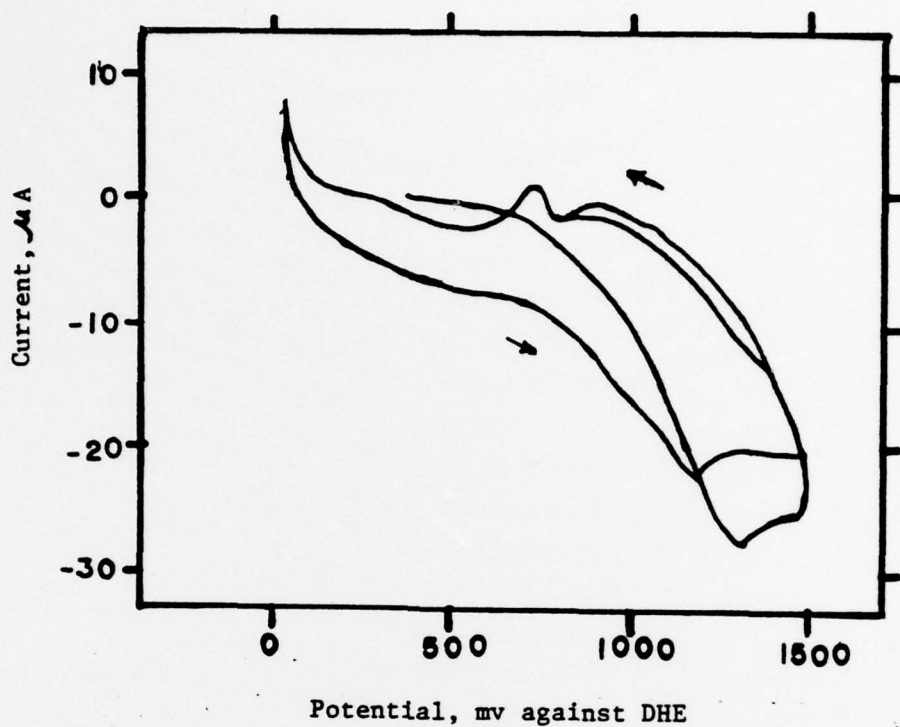

dl-10 Camphorsulfonic acid

| | |
|--------------------|----------------------|
| Concentration | 31% weight |
| Bubbler | Yes |
| Temperature | 80°C |
| Rest potential | 360 mV (Pt. vs. DHE) |
| Scan rate | 10mV/sec |
| Voltage range | 0 to 1.5 V |
| Quiescent solution | Yes |

Figure 7. Cyclic voltammogram of dl-10 camphorsulfonic acid

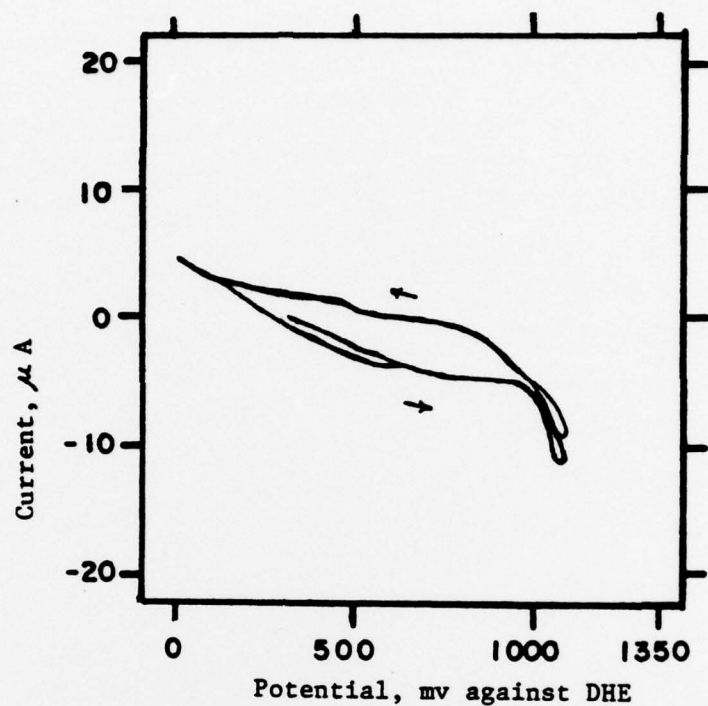

Heptafluorobutyric acid

| | |
|--------------------|----------------------|
| Concentration | 50% weight |
| Bubbler | No |
| Temperature | 80°C |
| Rest Potential | 300 mV (Pt. vs. DHE) |
| Scan rate | 50mV/sec |
| Voltage range | 0 to 1000mV |
| Quiescent solution | No |

Figure 8. Cyclic voltammogram of heptafluorobutyric acid.

Hydrogen was then used to purge the system for twenty minutes because of an unusually high rest potential (due to the presence of oxygen). Argon was used a second time to purge the system of hydrogen. Scanning in the positive direction the current increased steadily from 0 μA to -22 μA at which point the anodic potential was 1200 mV. The current then decreased slightly to -18 μA and the scan was reversed at 1500 mV. (The first scan gave a slightly higher current, -27 μA at 1300 mV.) The current increased to 1 μA where a cathodic reduction peak was observed at a potential of 725 mV. The current then dropped off to -2 μA and was nearly steady until zero potential was reached, where the current increase was due to hydrogen reduction. The reduction of current with successive sweeps indicated that some electroactive species were being removed.

The scan obtained with a 50% solution of heptafluorobutyric acid is given in figure 8. Scanning in the positive direction the current increased slightly from 0 μA at a rest potential of 300 mV to about -5 μA at 1000 mV; at this point the current increase was much sharper to a maximum of -11 μA at 1075 mV. The scan was reversed at this point. The current decreased in a regular fashion until a maximum of 5 μA was reached at approximate zero potential. This electrolyte appears to be reasonably stable electrochemically but its vapor pressure appears to be too high.

V. CONCLUSIONS AND DIRECTION OF FUTURE WORK

It appears possible at this point to eliminate certain classes from the list of potential electrolytes. These include aliphatic carboxylic acids and those carboxylic acids that are substituted with

chlorine and bromine. If the general property of aromatic sulfonic acids, if hydrolyzing in aqueous solution, is confirmed then this class will be eliminated.

Some fluorinated aliphatic acids such as hepta fluorinated butyric acid have several very desirable physical properties such as high specific conductance but their vapor pressures may be too high or at least the perfluorinated butyric acid vapor pressure is too high and it would be necessary to go to a C5 or C6 acid.

Certain sulfonic acids appear of interest such as sulfoacetic acid and 10-dl camphor sulfonic acid. The electrochemical stability of the latter is in question but a more pure material must be obtained for evaluation.

The tricarboxy acid, trimellitic, when used as the mono or di potassium salt appears to possess sufficient solubility and conductivity.

It is planned to study these compounds in more depth particularly in connection with the electrochemical properties referred to above. Then tests would include the employment of the compound in fuel cell type reactions.

The vapor pressure measurement is of critical importance in categorizing these electrolytes. Because of the limitations of the isopiestic method it is intended to go to a direct method for future measurements.

VI. REFERENCES

1. Power Systems Division, United Technologies Corporation "National Benefits Associated with Commercial Application of Fuel Cell Powerplants," Prepared for U.S. Energy Research and Development Administration under Purchase Order No. WA-76-3405, Feb. 27, 1976.
2. A. A. Adams, R.T. Foley, and R. M. Goodman, Interim Technical Report No. 4 on Contract No. DAAK02-72-C-0084.
3. A. W. Ralston, "Fatty Acids and Derivatives" John Wiley & Sons, New York (1948).
4. Saul Patai, Ed., "The Chemistry of Carboxylic Acids and Esters" John Wiley & Interscience 1969.
5. K. S. Markley, "Fatty Acids" Part 1, 2nd edition, Interscience 1961, "Fats and Oils" John Wiley 1964.
6. L. F. Fieser and M. Fieser, "Advanced Organic Chemistry" 3rd ed. Reinhold Publishing Corporation (1961)
7. M. Hudlicky, "Chemistry of Organic Fluorine Compounds" MacMillan 1962.
8. J. H. Simons, Ed., "Fluorine Chemistry" Academic Press 1954.
9. C. M. Suter, "Organic Sulfur Compounds" John Wiley 1944.
10. Earl Royal, "Advanced Organic Chemistry" Prentice Hall 1954.
11. International Critical Tables, Vol. VI., McGraw-Hill.
12. Landolt and Bernstein, "Physikalische Chemische Tabellen."
13. "International Union of Pure and Applied Chemistry: Dissociation of Organic Acids, etc.," Kortum et al., Butterworth 1961.
14. I. M. Heilbron, Ed., "Dictionary of Organic Compounds" Vol 1-5 Oxford University Press 1964.

15. T. Sarada, R.D. Granata, and R.T. Foley, "Materials of Construction and Electrode Materials for a Fuel Cell Using a Perfluoroalkane Electrolyte" Final Report on Contract EY-76-S-02-2879, April 1977.
16. R.A. Robinson and R.H. Stokes, "Electrolyte Solutions" Academic Press, New York (1955).
17. B.A. Soldane, R.W. Stoughton, R.J. Fox, and G. Scatchard, in "The Structure of Electrolyte Solutions" ed by W.J. Hamer, John Wiley & Sons, New York (1959).
18. R.H. Stokes and R.A. Robinson, Trans. Fara. Soc. 37, 419 (1941).
19. D.I. McDonald and J.R. Boyack, J. Chem. Eng. Data 14, 380 (1969).
20. Technical Bulletin IC/DP 239, Monsanto Co., 800 N. Lindbergh Blvd., St. Louis, Mo. 63166.
21. F. Fichter-Basel, Z. für Elektrochemie 20, 471, (1914).