

AD-A059 642

NORTHWESTERN UNIV EVANSTON ILL DEPT OF CHEMISTRY

F/G 7/2

RATIONAL SYNTHESIS OF UNIDIMENSIONAL MIXED VALENCE SOLIDS. STRU--ETC(U)

AUG 78 L D BROWN, D W KALINA, M S MCCLURE


N00014-77-C-0231

UNCLASSIFIED


TR-6

NL

1 OF 1
ADA
059642

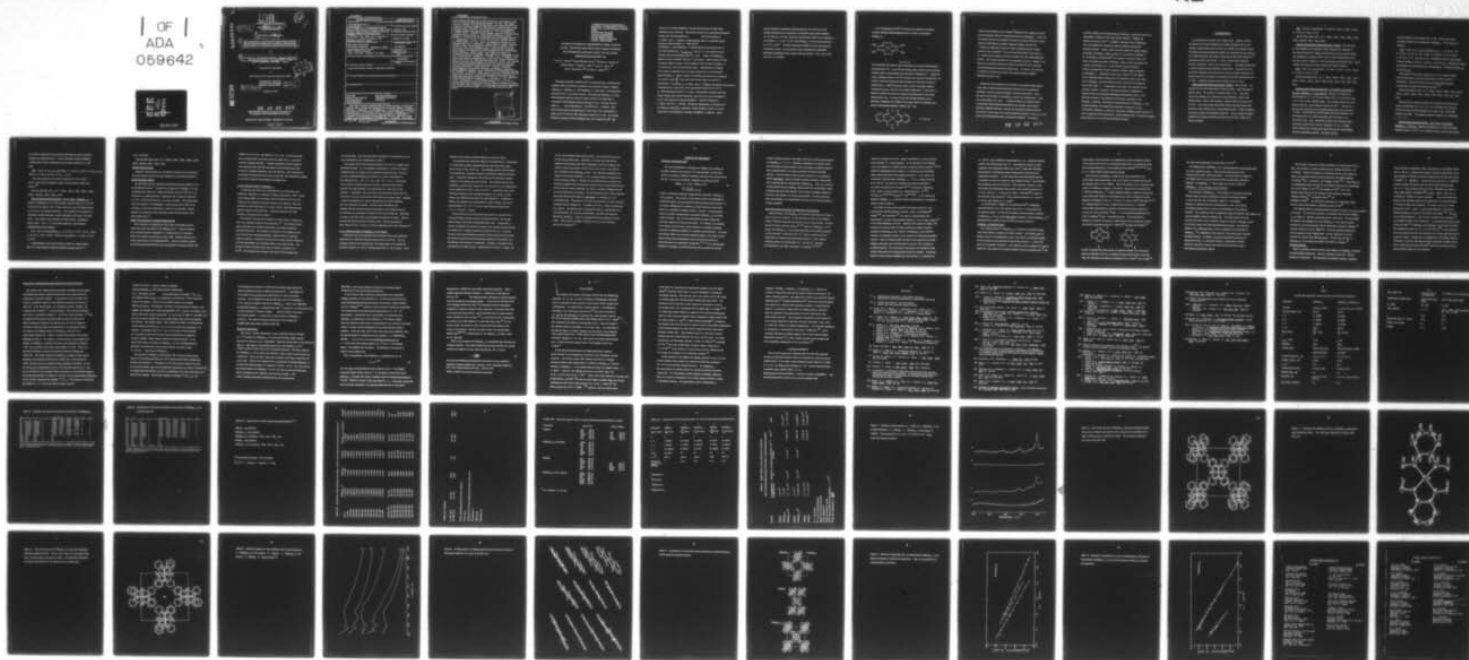

END
DATE
FILMED
12-78
DDC

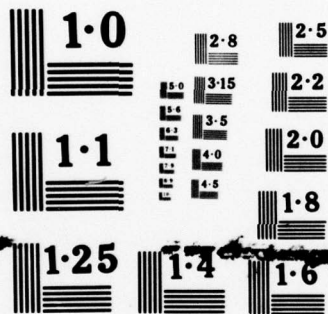

NATIONAL BUREAU OF STANDARDS
MICROCOPY RESOLUTION TEST CHART

AD A059642

LEVEL

OFFICE OF NAVAL RESEARCH

Contract N00014-77-C-0231
Task No. NR 053-640

14 TR-6

9 TECHNICAL REPORT NO. 6

6 Rational Synthesis of Unidimensional Mixed Valence Solids,
Structure-Oxidation State-Charge Transport Relationships
in Iodinated Nickel and Palladium Bisbenzoquinonedioximates.

by

10 Leo D. Brown, Davida Webster/Kalina, Malcolm S. McClure,
Steven Schultz, Stanley L. Ruby, James A. Ibers,
Carl R. Kannewurf, and Tobin J. Marks

Prepared for Publication

in


The Journal of the American Chemical Society

Northwestern University
Department of Chemistry
Evanston, Illinois 60201

11 22 Aug 78

August 22, 1978

12 68 p.

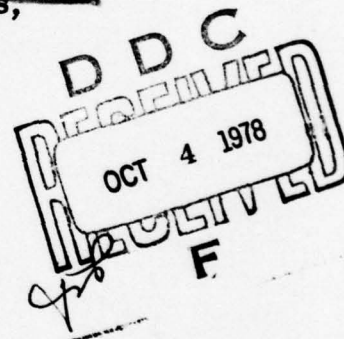

DDC FILE COPY

78 10 03 045

Reproduction in whole or in part is permitted for
any purpose of the United States Government

Approved for Public Release; Distribution Unlimited

260 805

alt

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 68 IS OBSOLETE
S/N 0102-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

least-squares refinement gave a final value of the conventional R index (on F) of 0.052 for 1278 reflections having $F_o^2 > 3\sigma(F_o^2)$. The crystal structure consists of stacked $\text{Pd}(\text{bqd})_2$ units, each staggered by 65° with respect to its nearest neighbors, and disordered chains of iodine atoms extending in the c-direction. The solvent molecules are disordered throughout tunnels which extend parallel to c. The Pd-Pd distance is $3.184(3)\text{\AA}$, Pd-N = $1.996(7)\text{\AA}$, and the $\text{Pd}(\text{bqd})_2$ units are rigorously planar. Resonance Raman studies ($\nu_o = 4880\text{--}6471\text{\AA}$) of $\text{Pd}(\text{bqd})_2\text{I}_{0.50}\cdot\text{S}$ and $\text{Ni}(\text{bqd})_2\text{I}_{0.5}\cdot\text{S}$ indicate that the predominant form of the iodine present is I_3^- ($\nu_{\text{fundamental}} = 107\text{ cm}^{-1}$), hence that the formal oxidation state of the $\text{M}(\text{bqd})_2$ units is $+0.17(2)$. Iodine -129 Mössbauer studies are also consistent with the I_3^- formulation. Optical spectra of these complexes exhibit a strong, broad transition at 600 nm which is largely, if not exclusively, due to the polyiodide chains. Crystallization of $\text{Ni}(\text{bqd})_2$ from benzene containing traces of iodine produces the new orthorhombic phase $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$. Single crystal x-ray studies have shown it to crystallize in the space group D_{2h}^{26} - Ibam with four formula units in a unit cell of dimensions $a = 16.438(2)$, $b = 14.759(4)$, and $c = 6.360(2)\text{\AA}$. Full-matrix least-squares refinement gave a final value of the conventional R index (on F) of 0.11 for 1026 reflections having $F_o^2 > 3\sigma(F_o^2)$. The structure contains rigorously planar $\text{Ni}(\text{bqd})_2$ units stacked along the c axis with each molecule staggered by 68° with respect to its nearest neighbors. The Ni-Ni distance is $3.180(2)\text{\AA}$ and Ni-N = $1.88(10)\text{\AA}$. Structural relationships are discussed for all $\text{M}(\text{bqd})_2$ and $\text{M}(\text{bqd})_2\text{I}_x$ compounds; partial oxidation results in a small contraction of the interplanar spacings of $0.019\text{\AA}(\text{Pd}) - 0.027\text{\AA}(\text{Ni})$. Single crystal electrical conductivity measurements (dc and 100 Hz ac) in the stacking direction show an increase in conductivity upon partial oxidation of $> 10^3$ (Ni) and $> 10^4$ (Pd). Maximum conductivities at 300°K are $\text{Ni}(\text{bqd})_2\text{I}_{0.50}\cdot 0.24\text{ toluene} = 1.1 \times 10^{-5} (\Omega\text{-cm})^{-1}$ and $\text{Pd}(\text{bqd})_2\text{I}_{0.5}\cdot 0.52\text{ o-dichlorobenzene} = 8.1 \times 10^{-3} (\Omega\text{-cm})^{-1}$. Variable temperature studies show that the electrical conductivity follows, over the entire range investigated, an exponential temperature dependence with a single activation energy: $0.54 \pm 0.08\text{ eV}(\text{Ni})$ and $0.22 \pm 0.03\text{ eV}(\text{Pd})$.

ACCESSION for	
NTIS	Write Section <input checked="" type="checkbox"/>
DDC	6-11 Section <input type="checkbox"/>
UNANNOUNCED	
DISPOSITION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
SPECIAL	
A	

unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Contribution from the Department of
Chemistry, the Department of Electrical
Engineering, and the Materials Research
Center.

Northwestern University
Evanston, Illinois 60201
and the Physics Division
Argonne National Laboratory
Argonne, Illinois 60439

RATIONAL SYNTHESIS OF UNIDIMENSIONAL MIXED VALENCE
SOLIDS. STRUCTURE-OXIDATION STATE-CHARGE TRANSPORT
RELATIONSHIPS IN IODINATED NICKEL AND PALLADIUM
BISBENZOQUINONEDIOXIMATES.

by Leo D. Brown,^{1a} Davida Webster Kalina,^{1a} Malcolm S. McClure,^{1b}
Steven Schultz,^{1c} Stanley L. Ruby,^{1c} James A. Ibers,^{*1a}
Carl R. Kannewurf,^{*1b} and Tobin J. Marks^{*1a, 2}


ABSTRACT

This paper presents a detailed study of crystal structure, stoichiometry, oxidation state, and electron transport in the materials $\text{Ni}(\text{bqd})_2$, $\text{Pd}(\text{bqd})_2$, $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$, $\text{Ni}(\text{bqd})_2\text{I}_{0.5}\cdot\text{S}$, and $\text{Pd}(\text{bqd})_2\text{I}_{0.5}\cdot\text{S}$, where bqd = o-benzoquinone-dioximato and S = an aromatic solvent. The compound $\text{Pd}(\text{bqd})_2\text{I}_{0.50}\cdot 0.52$ o-dichlorobenzene has been shown by single crystal X-ray diffraction to crystallize in the tetragonal space group $D_{4h}^{2-}P4/mcc$, with four formula units in a cell of dimensions $a = 16.048(7)$ and $c = 6.367(3)\text{\AA}$. Full-matrix least-squares refinement gave a final value of the conventional R index (on F) of 0.052 for 1278 reflections having $F_o^2 > 3\sigma(F_o^2)$. The crystal structure consists of stacked $\text{Pd}(\text{bqd})_2$ units, each staggered by 65° with

respect to its nearest neighbors, and disordered chains of iodine atoms extending in the \underline{c} -direction. The solvent molecules are disordered throughout tunnels which extend parallel to \underline{c} . The Pd-Pd distance is 3.184(3) Å, Pd-N = 1.996(7) Å, and the Pd(bqd)₂ units are rigorously planar. Resonance Raman studies ($\nu_0 = 4880\text{--}6471\text{ Å}$) of Pd(bqd)₂I_{0.50}·S and Ni(bqd)₂I_{0.5}·S indicate that the predominant form of the iodine present is I₃⁻ ($\nu_{\text{fundamental}} = 107\text{ cm}^{-1}$), hence that the formal oxidation state of the M(bqd)₂ units is +0.17(2). Iodine-129 Mössbauer studies are also consistent with the I₃⁻ formulation. Optical spectra of these complexes exhibit a strong, broad transition at 600 nm which is largely, if not exclusively, due to the polyiodide chains. Crystallization of Ni(bqd)₂ from benzene containing traces of iodine produces the new orthorhombic phase Ni(bqd)₂I_{0.02}. Single crystal x-ray studies have shown it to crystallize in the space group D_{2h}²⁶ - Ibam with four formula units in a unit cell of dimensions $\underline{a} = 16.438(2)$, $\underline{b} = 14.759(4)$, and $\underline{c} = 6.360(2)\text{ Å}$. Full-matrix least-squares refinement gave a final value of the conventional R index (on F) of 0.11 for 1026 reflections having $F_o^2 > 3\sigma(F_o^2)$. The structure contains rigorously planar Ni(bqd)₂ units stacked along the \underline{c} axis with each molecule staggered by 68° with respect to its nearest neighbors. The Ni-Ni distance is 3.180(2) Å and Ni-N = 1.88(10) Å. Structural relationships are discussed for all M(bqd)₂ and M(bqd)₂I_x compounds; partial oxidation results in a small contraction of the interplanar spacings of 0.019 Å(Pd) - 0.027 Å(Ni). Single

crystal electrical conductivity measurements (dc and 100 Hz ac) in the stacking direction show an increase in conductivity upon partial oxidation of $> 10^3$ (Ni) and $> 10^4$ (Pd). Maximum conductivities at 300° K are $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$ 0.24 toluene = $1.1 \times 10^{-5} (\Omega\text{-cm})^{-1}$ and $\text{Pd}(\text{bqd})_2\text{I}_{0.5} \cdot 0.52$ o-dichlorobenzene = $8.1 \times 10^{-3} (\Omega\text{-cm})^{-1}$. Variable temperature studies show that the electrical conductivity follows, over the entire range investigated, an exponential temperature dependence with a single activation energy: 0.54 ± 0.08 eV(Ni) and 0.22 ± 0.03 eV(Pd).

In an accompanying article³ we discuss the properties of stacked, partially oxidized bisdiphenylglyoximates of nickel and palladium, $M(dpg)_2I$, A.

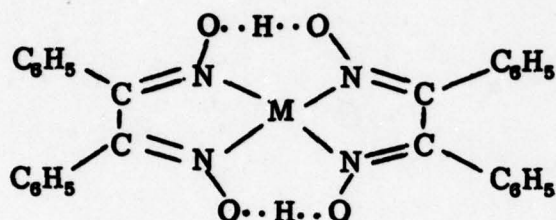


I

A

M = Ni, Pd

It was found that the iodine in these materials was present predominantly if not exclusively as I_3^- , hence that the $M(dpg)_2$ units possess formal fractional oxidation states, representable approximately as $[M(dpg)_2]_x^+ I_3^-$. Though the iodine oxidation produces a 10^7 - 10^8 increase in dc electrical conductivity, the facility of electron transport in these materials is still less than that of $K_2Pt(CN)_4Br_{0.3} \cdot 3H_2O$ ⁴ and several other classes of partially oxidized metallomacrocycles that we have recently synthesized.⁵ It was thus of interest to explore the effect of chemical functionalization on the metal bisglyoximate core. A means to decrease stacking distances and to elaborate conjugation was evident in the planar nickel and palladium complexes of benzoquinonedioxime, $M(bqd)_2$, B.⁶ The

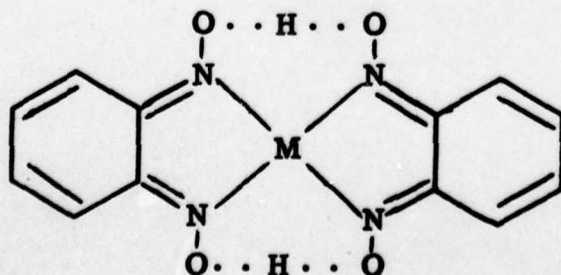

B

M = Ni, Pd

earlier work of Keller and co-workers^{7,8} established the existence of quasi-one-dimensional materials of reported stoichiometry $M(bqd)_2I_{0.5}$, $M=Ni, Pd$. The nickel complex was reported to possess a tetragonal ($P4/mcc$) crystal structure with stacks of partially staggered $Ni(bqd)_2$ units ($Ni-Ni = 3.153(3)\text{\AA}$) and disordered chains of iodine-containing species running parallel to the c direction.⁸ It was proposed that iodine was present as I_3^- , though this conclusion could not be derived from the Bragg diffraction pattern. The crystal structure of the uniodinated precursor, $Ni(bqd)_2$, was found to be monoclinic ($P2_1/n$) by Leichert and Weiss⁹ and to consist of canted bis(benzoquinonedioximato)nickel units. In contrast, the structure of $Pd(bqd)_2$ is orthorhombic ($Imcb$) with stacked $Pd(bqd)_2$ moieties extending along the c axis.

Though the aforementioned work provided an important initial glimpse of the range of bisbenzoquinonedioximate structures and compositions obtainable, several important questions remained unanswered. First, the nature of the iodine in the $M(bqd)_2I_{0.5}$ species was undetermined. Thus, it was impossible to say with certainty whether the iodinated nickel and palladium bisbenzoquinonedioximates were actually mixed valence (partially oxidized) materials. Second, the available structural data did not provide a clear picture as to what geometrical changes, if any, (e.g., in the metal-metal stacking distances) accompanied iodination. The canted

78 10 03 045

monoclinic $\text{Ni}(\text{bqd})_2$ and stacked tetragonal $\text{Ni}(\text{bqd})_2\text{I}_{0.5}$ structures could not be meaningfully compared in the sense that the stacked $\text{Ni}(\text{dpg})_2$ and $\text{Ni}(\text{dpg})\text{I}$ structures could.³ In addition, structural data on $\text{Pd}(\text{bqd})_2\text{I}_{0.5}$ were not available for comparison with the existing orthorhombic $\text{Pd}(\text{bqd})_2$ structure. Finally, little was known about the charge transport properties of $\text{M}(\text{bqd})_2\text{I}_{0.5}$ single crystals vis-à-vis those of $\text{M}(\text{bqd})_2$.¹¹ In a preliminary communication¹² we reported a resonance Raman and iodine-129 Mössbauer study of $\text{Ni}(\text{bqd})_2\text{I}_{0.5}$ which showed the iodine to be present predominantly as I_3^- , hence that the charge distribution could be represented by formal fractional oxidation states as depicted by $[\text{Ni}(\text{bqd})_2]_x^+ \text{I}_3^-$. Independent of this work, analysis¹³ of the diffuse X-ray scattering pattern arising from the disordered iodine chain structure in $\text{Ni}(\text{bqd})_2\text{I}_{0.5}$ reached exactly the same conclusion concerning the form of the iodine: I_3^- . In this paper we present a full exposition of our chemical, spectral, structural, and charge transport investigations within the nickel and palladium bisbenzoquinonedioximate series. This discussion includes a reformulation of the actual composition of the $\text{M}(\text{bqd})_2\text{I}_{0.5}$ materials, the structural characterization of $\text{Pd}(\text{bqd})_2\text{I}_{0.5} \cdot 0.52$ o-dichlorobenzene, the synthesis and structure elucidation of a new, orthorhombic $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ compound, comments on $\text{M}(\text{bqd})_2\text{I}_x$ optical spectra,¹⁴ and a comparison of the geometrical, partial oxidation state, and charge transport characteristics in all of the aforementioned materials.

EXPERIMENTAL

All solvents and chemicals were reagent grade. Benzene, toluene, and hexane were freshly distilled from sodium-potassium alloy under nitrogen; *o*-dichlorobenzene was dried over Davison 4A molecular sieves. The ligand *o*-benzoquinonedioxime (bqdH) was synthesized by the reduction of *o*-dinitrosobenzene with sodium borohydride as described elsewhere.¹⁵ Elemental analyses were by Ms. H. Beck, Northwestern Analytical Services Laboratory, Micro-Tech Laboratories, Galbraith Laboratories, or Alfred Bernhardt Microanalytical Laboratories. Analysis of Ni and I by neutron activation was performed by General Activation Analysis, Inc. Mass spectra were recorded on a Hewlett-Packard 5930 instrument by Dr. D. Hung. Iodinated materials were routinely stored at -20° C.

Bis(benzoquinonedioximato)nickel(II), Ni(bqd)₂. This complex was prepared by the room temperature reaction of $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$ with bqdH in ethanol-water. The reaction is complete within 0.5 hr. The crude, dark-brown Ni(bqd)_2 was collected by suction filtration, washed with distilled water, washed with methanol, and then dried for several hours at 110°C. The crude product was finally Soxhlet extracted (twice) with benzene to yield a dark-brown, microcrystalline solid. Yields of Ni(bqd)_2 from this procedure were typically about 80%. Large crystals (elongated platelets) for transport studies were grown by very slow cooling of hot toluene solutions.

Anal. Calcd for $C_{12}H_{10}N_4O_4Ni$: C, 43.28; H, 3.03; N, 16.83. Found: C, 43.21; H, 2.96; N, 16.74.

Infrared data (Nujol mull, cm^{-1}): 3090w, 1600s, 1500s, 1265s, 1140m, 1080s, 950s(br), 820w, 740vs, 610m.

Bis(benzoquinonedioximato)palladium(II), $Pd(bqd)_2$. The procedure for the synthesis and purification of this compound was analogous to that described above for $Ni(bqd)_2$ except that the $PdCl_2$ starting material was solubilized by treatment with a small amount of hydrochloric acid. The final product, $Pd(bqd)_2$, is a dark-green microcrystalline solid. Larger crystals can be grown by slow cooling of hot toluene solutions.

Anal. Calcd. for $C_{12}H_{10}N_4O_4Pd$: C, 37.86; H, 2.65; N, 14.72. Found: C, 37.78; H, 2.60; N, 14.68.

Infrared data(Nujol mull, cm^{-1}): 1600s, 1520vw, 1490s, 1415s, 1355s, 1285vs, 1185m, 1165m, 1130w, 1060vs, 965w, 880m, 790m, 740s, 730s, 615m.

Bis(benzoquinonedioximato)palladium · 0.50 iodine · 0.52 o-dichloro-benzene, $Pd(bqd)_2 \cdot I_{0.50} \cdot 0.52 o-C_6H_4Cl_2$. Solutions of $Pd(bqd)_2$ in o-dichlorobenzene ($4.5 \times 10^{-3}M$) were heated to $90^\circ C$ and were then made $4.0 \times 10^{-2}M$ in triply sublimed iodine. The resulting mixture was next filtered while hot, and the filtrate rewarmed to $90^\circ C$. The hot solution was then allowed to cool to ambient temperature over a period of 3-5 days. At this time the cooled solution was suction-filtered, and the solid product was washed repeatedly with cold hexane, and then dried in air. Dark, needle-like crystals of the desired product possessed a golden luster and were typically 3-15 mm. in length. These crystals were mechanically separated from the noncrystalline and microcrystalline material. The yield of golden

crystals obtained in this manner was ca. 40%. On the basis of the elemental analysis, the stoichiometry $\text{Pd}(\text{bqd})_2\text{I}_{0.5} \cdot 0.52 \text{ } o\text{-C}_6\text{H}_4\text{Cl}_2$ is assigned.

Anal. Calcd. for $\text{C}_{15.12}\text{H}_{12.08}\text{N}_4\text{O}_4\text{PdI}_{0.5}\text{Cl}_{1.04}$: C, 34.91; H, 2.34; N, 10.78; I, 12.13; Cl, 7.06. Found: C, 34.56; H, 2.34; N, 10.82; I, 12.19; Cl, 7.09. Analyses (C, H, N, Bernhardt) on each of three single crystals weighing 0.372 mg., 0.500 mg., and 0.675 mg., indicated an average incorporation of o-dichlorobenzene corresponding to: $\text{Pd}(\text{C}_6\text{H}_5\text{N}_2\text{O}_2)_2\text{PdI}_{0.52(2)}(\text{ } o\text{-C}_6\text{H}_4\text{Cl}_2)_{0.41(2)}$.

Mass spectra of the above crystals (10 or 70 eV ionizing voltage) recorded with source and probe temperatures of 200°C and 100°C, respectively, revealed the parent ions and fragmentation patterns characteristic of iodine and o-dichlorobenzene. ^{16a}

Infrared data (Nujol mull, cm^{-1}): 1600s, 1520vw, 1490s, 1415s, 1355s, 1280vs, 1185m, 1160m, 1130w, 1065vs, 970w, 880w, 790w, 740s, 730s, 615m.

When the above synthetic procedure was carried out with increased iodine concentrations (4.9, 5.9, 6.9, $7.9 \times 10^{-2}\text{M}$) the yield of golden crystals decreased and the appearance of a dark, shiny, rather flaky material was noted. By elemental analysis it appears to be $\text{Pd}(\text{bqd})_2\text{I}_x$ $x = 1.5 - 2.0$.

Bis(benzoquinonedioximato)nickel · 0.52 iodine · 0.32 toluene,
 $\text{Ni}(\text{bqd})_2\text{I}_{0.52} \cdot 0.32 \text{ C}_7\text{H}_8$. Solutions of $\text{Ni}(\text{bqd})_2$ ($6.0 \times 10^{-3}\text{M}$) and triply sublimed iodine ($4.0 \times 10^{-2} - 4.4 \times 10^{-2}\text{M}$) in toluene at 90°C were treated

in a manner analogous to the previously described procedure involving $\text{Pd}(\text{bqd})_2$ in *o*-dichlorobenzene. Large needle-like crystals exhibiting a golden luster could be isolated from the toluene solutions in ca. 20% yield.

Anal. Calcd. for $\text{C}_{14.24}\text{H}_{12.56}\text{N}_4\text{O}_4\text{NiI}_{0.52}$: C, 39.92; H, 2.96; N, 13.08; I, 15.40. Found: C, 37.60; H, 2.74; N, 13.07; I, 15.49.

The mass spectrum of the above crystals (10 or 70 eV, 200°C source, 100°C probe) exhibited a pattern characteristic of iodine and toluene.^{16b}

Infrared data(Nujol mull, cm^{-1}): 3090w, 1600s, 1500s, 1265s, 1160m, 1080vs, 980w(br), 830m, 740vs, 615m.

Bis(benzoquinonedioximato)nickel · 0.0177 iodine, $\text{Ni}(\text{bqd})_2\text{I}_{0.0177}$. A solution of $\text{Ni}(\text{bqd})_2$ ($6.2 \times 10^{-3}\text{M}$) and triply sublimed iodine ($1.4 \times 10^{-2}\text{M}$) in benzene was heated to 78°C, filtered while hot, and the filtrate allowed to cool slowly to ambient temperature. The resulting dark crystals were collected by suction filtration, washed repeatedly with hexane, and dried in air. The crystals of this material are dark needles, exhibiting no golden luster. The C, H, N elemental analysis is experimentally indistinguishable from $\text{Ni}(\text{bqd})_2$.

Anal. Calcd. for $\text{C}_{12}\text{H}_{10}\text{N}_4\text{O}_4\text{NiI}_{0.0177}$: C, 43.00; H, 3.01; N, 16.72. Found: C, 43.45; H, 3.25; N, 16.23. Calcd for $\text{C}_{12}\text{H}_{10}\text{N}_4\text{O}_4\text{Ni}$: C, 43.28; H, 3.03; N, 16.83.

A determination of the ratio of nickel to iodine in a single crystal (the X-ray data crystal) by neutron activation analysis gave Ni : I =

1.00 : 0.0177(73).

Infrared data (Nujol mull, cm^{-1}): 3090w, 1600s, 1500s, 1265s, 1140m, 1080s, 950s(br), 820w, 740vs, 610m.

Spectral Measurements

Infrared, resonance Raman, and electronic spectra were recorded in the same manner and with the same apparatus as described previously.³

Iodine Mössbauer Studies

The apparatus and data acquisition/analysis procedures employed were as described previously.³ Samples were prepared by weighing ca. 70 mg. of $\text{Ni}(\text{bqd})_2$ into a small vial, adding the desired amount of $^{129}\text{I}_2$ ³ in 1-2 ml. of benzene or *o*-dichlorobenzene, capping the vial, heating the mixture to ca. 80° C, and then allowing it to cool slowly overnight. The solid product was next collected by centrifugation, washed several times with 1-2 ml. of hexane, and was then dried under a stream of dry nitrogen. Several samples were prepared which elemental analysis showed to have a Ni:I ratio greater than 1.0.

Single Crystal Electron Transport Measurements

The procedures and apparatus for four-probe conductivity measurements were those described for the $\text{M}(\text{dpg})_2\text{I}$ work.³ Contact materials were colloidal graphite suspended in 1,3-butylene glycol or Demetron M8001 cold-setting conductive gold contact paint. Results with these two contact preparations were indistinguishable. Typical crystalline samples of the bisbenzoquinonedioxmats were approximately tetragonal needles with

lengths of 2.0-4.0 mm. and widths of 0.1-0.3 mm. All measurements were conducted with current flow along the needle axis, i. e., along the molecular stacking direction. Variable temperature studies employed measurements taken with both increasing and decreasing temperature to check for possible hysteresis; none was observed. Room temperature conductivity measurements were always made after high temperature studies to ascertain if sample decomposition was taking place.

X-Ray Diffraction Study of $\text{Ni}(\text{bqd})_2 \cdot \text{I}_{0.02}$

Preliminary film data were consistent with Laue symmetry mmm. Systematic extinctions are indicative of space groups Ibam or Iba2 . Based on the setting angles of 14 manually centered reflections ($40 \leq 2\theta \leq 60^\circ$, $\text{CuK}\alpha$) the cell constants presented in Table I were obtained. Data were collected at room temperature on a Picker FACS-1 diffractometer using methods general in this laboratory. Important features of the data collection are summarized in Table I.

The structure was solved and refined in a facile manner, using procedures and computer programs described before.¹⁷ The centrosymmetric space group Ibam was assumed on the basis of excellent agreement among Friedel pairs. The positions of the atoms of the $\text{Ni}(\text{bqd})_2$ species were obvious from a three-dimensional, origin-removed, sharpened Patterson function. Included in the final cycle of least-squares refinement were the contributions from hydrogen atoms on the carbon atoms. The positions of these hydrogen atoms were calculated, assuming $\text{C-H} = 0.95 \text{ \AA}$. The hydrogen atom position in the $\text{O}(1)\text{-H-O}(2)$ hydrogen bond

was not included. This final refinement converged to R indices and an error in an observation of unit weight given in Table I.

Examination of the final agreement between $|F_o|$ and $|F_c|$ reveals some disturbing features; (1) The highest residual peak of 1.36 e/A³ is located at $\frac{1}{2}00$, but there is a general level of density along the $\frac{1}{2}0z$ line; (2) There are some outstanding differences between $|F_o|$ and $|F_c|$ especially for hk0 reflections (e.g., 510: 8.7, 25.0; 330: 12.3, 1.9 e⁻). On the basis of the neutron activation analysis of the data crystal (see above) there appears to be approximately 0.02 iodine atoms per nickel atom in the material. Presumably, the iodine atoms are positioned along the $\frac{1}{2}0z$ row, since there are large channels there that could accommodate iodine. Although a number of attempts were made to approximate the iodine scattering, none was especially successful. However these calculations did establish that the overall structural parameters of the Ni(bqd)₂ portion of the structure are insensitive to models for the iodine scattering. Ultimately we chose as the final model one that ignores the presence of iodine. Table II presents the final parameters from this model. Table III presents the final listing of $10|F_o|$ vs $10|F_c|$ for those reflections used in the refinement.¹⁸

X-ray Diffraction Study of Pd(bqd)₂I_{0.50} · 0.52 C₆H₄Cl₂

Preliminary film data indicated Laue symmetry 4/mmm and systematic extinctions are consistent with space groups P4/mcc and P4cc. The cell constants (Table I) were obtained from the setting angles of 15 reflections manually centered on a FACS-1 diffractometer (30° < 2θ < 40°, MoKα₁). Other

features of the crystal and data collection are given in Table I.

The structure was solved and refined as described above. Examination of Friedel pairs strongly suggested that the centrosymmetric space group $P4/mcc$ is the correct one. The $Pd(bqd)I_x$ portion of the structure was located from a Patterson function and subsequent difference Fourier maps. In the final refinement of this portion of the structure variable occupancy of the iodine atom was included. The resultant formula was $Pd(bqd)_2I_{0.444}$ and the final values of R , wR , and an error in an observation of unit weight were 0.070, 0.102, and $3.63 e^-$. Again there were some individual examples of poor agreement between $|F_o|$ and $|F_c|$, in this instance not restricted primarily to the $hk0$ reflections. A difference Fourier map showed as its main features a peak of height $1.28 e/A^3$ at approximately 0.06, 0.13, 0.15 and a ring of electron density about $x = 0$, $y = 0$ in the $z = \frac{1}{2}$ plane.


At this point it was discovered (see above) that the crystals of this compound contain varying amounts of *o*-dichlorobenzene, the average amount being 0.52 solvent molecule/palladium atom. Consequently, a number of attempts were made to account for the residual electron density as arising from a variable amount of *o*- $C_6H_4Cl_2$ in the $0,0,z$ channel. Because of the 4-fold symmetry imposed on this channel and the fact that the solvent molecule does not intrinsically possess such symmetry, the disordering of the solvent is considerable. Although a calculation of the contributions of a $C_6H_4Cl_2$ rotor, constrained to lie in the $z = \frac{1}{2}$ plane, led

to some improvement between $|F_o|$ and $|F_c|$, this model did not account for the main residual peak. Ultimately, a Cl atom was placed at the position of this residual peak and in subsequent cycles the occupancy and isotropic thermal parameter of this Cl atom were varied, along with the other variables of the $\text{Pd}(\text{bqd})_2\text{I}_x$ portion. This refinement ultimately converged to the formula $\text{Pd}(\text{bqd})_2\text{I}_{0.48} \cdot 0.91$ o-dichlorobenzene and agreement indices present in Table I. Because of correlation between occupancy and thermal parameter of the Cl atom and because of the very approximate nature of the model for solvent scattering, the ratio of solvent to $\text{Pd}(\text{bqd})_2\text{I}$ derived from these data is very uncertain. We will henceforth refer to this compound, based upon the elemental analysis (vide supra), as $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52$ o-dichlorobenzene. Placement of a Cl atom at this position is made chemically reasonable by the resultant Cl...Cl distance of 3.05 Å, a value to be expected in o-C₆H₄Cl₂. The improvement in agreement indices is considerable as is more importantly, the removal of outstanding, individual discrepancies between $|F_o|$ and $|F_c|$. Table IV presents the final parameters from this model. Table V gives a listing of 10 $|F_o|$ vs 10 F_c for the reflections used in the refinement.¹⁸

RESULTS AND DISCUSSION

Chemistry and Stoichiometry

The slow crystallization of $\text{Ni}(\text{bqd})_2$ and $\text{Pd}(\text{bqd})_2$ from certain hot aromatic solvents in the presence of an approximately 10-fold molar excess of I_2 produces iodinated crystalline materials with a golden luster (eq. (1)). In the case of $\text{Pd}(\text{bqd})_2$, iodination in o-dichlorobenzene



$\text{M} = \text{Ni, Pd}$

$\text{S} = \text{aromatic solvent}$

yields a crystalline compound of approximate composition $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52 \text{ } \text{o}\text{-C}_6\text{H}_4\text{Cl}_2$. The presence of the solvent could be demonstrated by elemental analysis and mass spectrometry (see Experimental Section). In our hands, $\text{Ni}(\text{bqd})_2$ was too soluble in o-dichlorobenzene to give good yields of a crystalline iodination product. However in toluene, golden lustrous crystals of approximate composition $\text{Ni}(\text{bqd})_2\text{I}_{0.32} \cdot 0.32 \text{ toluene}$ could be isolated. The solvent incorporation was again assigned by elemental analysis and mass spectrometry. For $\text{Pd}(\text{bqd})_2$, the solubility in hot toluene was too small to allow isolation of crystalline iodinated materials in sufficient quantities for complete characterization. The above formulations differ from previous iodination studies on the nickel and palladium bisbenzoquinonedioximates where solvent incorporation (o-dichlorobenzene) was apparently not detected.^{7,8,13} In our experiments, iodination of $\text{Pd}(\text{bqd})_2$ in o-dichlorobenzene with a greater than 10-fold

excess of iodine produced a dark flaky solid which analyzed approximately as $\text{Pd}(\text{bqd})_2\text{I}_x$, $x = 1.5-2.0$. Iodination of $\text{Ni}(\text{bqd})_2$ in hot benzene with a two-fold excess of iodine yielded a dark (not golden) crystalline material which contained little or no iodine according to standard elemental analyses. For the crystal of this material chosen for X-ray diffraction studies (vide infra), neutron activation analysis revealed a nickel/iodine ratio consistent with the stoichiometry $\text{Ni}(\text{bqd})_2\text{I}_{0.08}$. Thus, our chemical results indicate that the $\text{M}(\text{bqd})_2\text{I}_x$ stoichiometry has considerably greater variability than previously thought, both in terms of halogen content and in terms of the tendency for solvent incorporation. It will be seen that both characteristics are understandable in terms of the crystal structures of these materials.

Resonance Raman and Iodine-129 Mössbauer Measurements

Raman spectra of the $\text{M}(\text{bqd})_2\text{I}_x \cdot n\text{S}$ materials are presented in Figure 1; data are set out in Table VI. As was discussed in depth for the $\text{M}(\text{dpg})_2\text{I}$ studies,³ different polyiodide species give rise to characteristic, resonant-enhanced Raman scattering spectra.^{5a, 19} Spectra of $\text{Ni}(\text{bqd})_2\text{I}_{0.52} \cdot 0.32$ toluene and $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52$ *o*-dichlorobenzene are essentially identical; a strong emission is observed at 107 cm^{-1} and an overtone at 215 cm^{-1} . These bands are absent in the uniodinated materials. Such a Raman scattering pattern is characteristic of I_3^- , the 107 cm^{-1} vibration corresponding to the totally symmetric I-I-I stretch.^{5a, 19, 20}

There is no evidence for free I_2 , weakly coordinated I_2 , or any more than trace amounts of I_3^- in these spectra. As was discussed in the $M(dpg)_2I$ work, such species are readily detected in resonance Raman spectra.^{3, 5a, 19} Unlike the diphenylglyoximate systems, no scattering from the $M(bqd)_2$ units could be discerned in the iodinated materials. In the iodine-rich compounds of stoichiometry $Pd(bqd)_2I_x$, $x = 1.5-2.0$, strong scattering at ca. 180 cm^{-1} was observed, indicative of weakly coordinated I_2 , as found in the structures and spectra^{5a, 19} of materials containing I_2 and I_3^- units in close proximity (e. g. $(phenacetin)_2H^+I_3^- \cdot I_2$ ^{3, 21a}, $(Cs^+)_2(I_3^-)_2 \cdot I_2$,^{5a, 19, 21b} $(C_2H_5)_4N^+I_3^- \cdot 2I_2$ ^{5a, 19, 21c}). In the iodine-poor material, $Ni(bqd)_2I_{0.018}$, no Raman scattering attributable to a polyiodide species could be observed.

In an effort to explore the possibility that Raman-inactive I^- was present in the iodinated $M(bqd)_2$ materials, iodine - 129 Mössbauer²² studies^{3, 5a} were undertaken.¹² In a cubic or approximately cubic environment, I^- gives a characteristic singlet ($\delta = -0.51\text{ mm/sec}$, $e^2qQ=0$)²² in the iodine Mössbauer spectrum. Because of the expense of iodine - 129 and the very large excesses of iodine necessary to prepare practical quantities of $Ni(bqd)_2I_{0.52} \cdot 0.32$ toluene or $Pd(bqd)_2I_{0.50} \cdot 0.52$ *o*-dichlorobenzene as crystalline samples, it was necessary to study polycrystalline powders. Several iodinated nickel specimens were prepared by stirring $Ni(bqd)_2$ compounds with a stoichiometric amount of $^{129}I_2$ in benzene or *o*-dichlorobenzene, then removing the supernatant and washing the solid product with pentane (see Experimental Section for details). The Raman spectra of these samples exhibited the characteristic I_3^- fundamental at

ca. 108 cm^{-1} and no evidence of appreciable I_3^- or I_2 . Elemental analysis showed a Ni:I ratio greater than 1.0. The Mössbauer spectra of these materials were somewhat broader than normal,³ apparently reflecting macroscopic or microscopic sample inhomogeneity arising from the preparative procedure. For this reason the derived polyiodide spectral parameters are not as accurate as in the $\text{M}(\text{dpg})_2\text{I}$ studies,³ and exhaustive data refinement was not carried out. Most important, however, is the information these Mössbauer data provide on the possible presence of I^- or, also, free I_2 ($\delta \approx +0.98\text{ mm/sec}$, $e^2qQ \approx -1586\text{ MHz}$).²² A conservative estimate of the amount of I^- which could be present is ca. 3 mole %; for free I_2 , this number is ca. 5 mole%.


As already noted, a diffuse X-ray scattering study¹³ of $\text{Ni}(\text{bqd})_2\text{I}_{0.5}$ concluded that the form of the iodine present was I_3^- in agreement with our spectral results. We find that the diffuse scattering pattern exhibited by $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52\text{ O} \cdot \text{C}_6\text{H}_4\text{Cl}_2$ (vide infra) is identical to that of $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$,¹³ indicating that an identical form of iodine is present, namely I_3^- .

$\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ Crystal Structure

The crystal structure of $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ is composed of individual $\text{Ni}(\text{bqd})_2$ units which exhibit no unusual non-bonded contacts. The $\text{Ni}(\text{bqd})_2$ units are stacked along the crystallographic c -axis, such that the coordination planes of the Ni atoms are perpendicular to the stacking direction. A view of the unit cell is presented in Figure 2. Each $\text{Ni}(\text{bqd})_2$ moiety is staggered by approximately 68° with respect to its nearest neighbors along the stacking axis.²³ The

iodine atoms, whose presence was established by neutron activation analysis of the crystal used in the X-ray diffraction experiment, are presumed, based upon analogous structures, to be positioned in the channels^{3,5a,7,8,13} along $\frac{1}{2}$, 0, z, which exhibit residual electron density.

The Ni atoms in $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ occupy the 4c special positions in the orthorhombic space group *Ibam*; thus, all Ni atoms are equally spaced along the stacking axis by $c/2$ ($3.180(2)\text{\AA}$). This Ni-Ni distance can be compared with values of $3.856(2)\text{\AA}$ for $\text{Ni}(\text{bqd})_2$ (a monoclinic, slipped-stack structure)⁹ and $3.153(3)\text{\AA}$ for $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$.⁸ Partial oxidation typically results in a contraction in the metal-metal distance as illustrated by the nickel metallomacrocycles $\text{Ni}(\text{dpg})_2$ and $\text{Ni}(\text{dpg})_2\text{I}$ (3.547\AA vs. $3.271(1)\text{\AA}$),³ as well as NiPc ²⁴ and NiPcI ,^{5a,e,f} Pc = phthalocyanine (4.79\AA for a slipped-stack structure vs. $3.244(3)\text{\AA}$). Nickel-nickel separations for stacked, unoxidized glyoximate systems are as short as 3.24\AA in $\text{Ni}(\text{CHD})_2$,²⁵ CHD = 1,2-cyclohexanedionedioximato and 3.25\AA in $\text{Ni}(\text{dmg})_2$,²⁶ dm = dimethylglyoximato. The shortest Ni-Ni distances are found in the dimeric, eclipsed face-to-face structures of nickel macrocyclic compounds A (Ni-Ni = $3.063(1)\text{\AA}$)²⁷ and B (Ni-Ni = $2.788(2)\text{\AA}$).²⁸

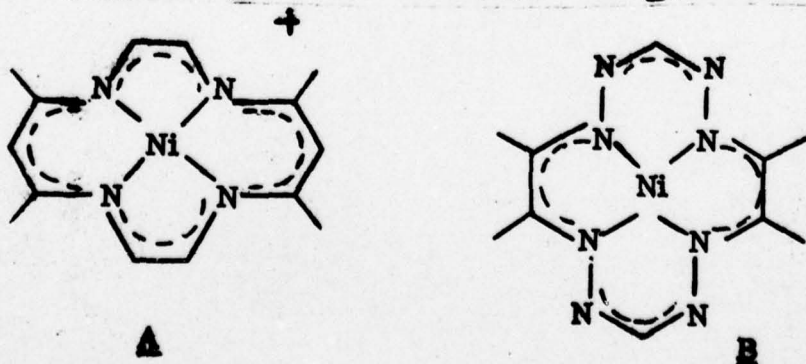

In these complexes the nickel atoms are displaced slightly out of the ligand planes (as defined by the four coordinated nitrogen atoms) toward each other. Thus, the interplanar spacings are estimated to be 3.19\AA (A)²⁷ and 3.00\AA (B).²⁸

The metal-metal separation in nickel metal is 2.49 \AA .²⁹

The $\text{Ni}(\text{bqd})_2$ unit in $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ has crystallographically imposed symmetry $2/m$ and is therefore planar. Figure 3 shows the structure of the molecule and the atom numbering scheme. The bond lengths and angles in the $\text{Ni}(\text{bqd})_2$ unit are in good agreement with the parameters reported in $\text{Ni}(\text{bqd})_2$ ⁹, and $\text{Ni}(\text{bqd})_2\text{I}_{0.5}$.⁸ These values are set out in Table VII.

$\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52 \text{ o-C}_6\text{H}_4\text{Cl}_2$ Crystal Structure

The structure of $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52 \text{ o-C}_6\text{H}_4\text{Cl}_2$ is composed of individual $\text{Pd}(\text{bqd})_2$ units and I atoms exhibiting no unusual non-bonded contacts.

A view of the unit cell is presented in Figure 4. The $\text{Pd}(\text{bqd})_2$ moieties are stacked along the crystallographic c -axis, such that the coordination planes of the Pd atoms are perpendicular to the stacking direction. Each $\text{Pd}(\text{bqd})_2$ moiety is staggered by approximately 65° with respect to its nearest neighbors along the stacking axis. The iodine atoms also stack one above the other in the c direction, filling the "tunnels" along $\frac{1}{2}z$ created by the benzo rings of the benzoquinonedioximato ligands. The observed diffuse X-ray scattering pattern, which is identical to that reported for $\text{Ni}(\text{bqd})_2\text{I}_{0.5}$,¹³ is attributable to the disorder of the iodine atoms along the stacking direction. In addition, the o -dichlorobenzene molecules are believed to reside, in a disordered fashion, in the tunnels of larger diameter (along $00z$) created by the oxygen atoms and benzo rings of the benzoquinonedioximato ligands.

The Pd atoms occupy the 4f special positions in the space group $P4/mcc$; thus, all Pd atoms are equally spaced along the stacking direction by $c/2$ (3.184(3) Å). This Pd-Pd distance is comparable with the Pd-Pd distances found in the partially oxidized stacked glyoximate compounds $\text{Pd}(\text{gly})_2\text{I}$ (3.244(1) Å),³⁰ $\text{gly} = \text{glyoximate}$, and $\text{Pd}(\text{dpg})_2\text{I}$ (3.26 Å)^{31a,b}. These distances are significantly shorter than the Pd-Pd distances found in the corresponding precursors $\text{Pd}(\text{gly})_2$ (3.558 Å)³² and $\text{Pd}(\text{dpg})_2$ (3.52 Å)^{31c} and is only slightly longer than the Pd-Pd distances in the unoxidized complexes $\text{Pd}(\text{bqd})_2$ (3.202(1) Å);¹⁰ $\text{Pd}(\text{dmg})_2$ (3.253 Å),²⁶ and $\text{Pd}(\text{CHD})_2$ (3.250 Å)²⁵. All of the above distances are considerably longer than the metal-metal distance in palladium metal (2.75 Å).²⁹

The $\text{Pd}(\text{bqd})_2$ unit has crystallographically imposed symmetry 2/m and is required to be planar. The molecular geometry is essentially that shown for $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ in Figure 3; the atom numbering scheme is the same. The bond lengths and angles in the $\text{Pd}(\text{bqd})_2$ unit of the $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52 \text{ o-C}_6\text{H}_4\text{Cl}_2$ crystal structure are in good agreement with the parameters reported in $\text{Pd}(\text{bqd})_2$,¹⁰ and these values are given in Table VII. The most significant differences in the parameters of the $\text{Pd}(\text{bqd})_2$ units in the two structures are in the Pd-N(1)-C(1) and Pd-N(2)-C(2) bond angles, 114.0(6)° and 115.8(6)° in $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52 \text{ o-C}_6\text{H}_4\text{Cl}_2$ and 122(1)° and 124(1)° in $\text{Pd}(\text{bqd})_2$.¹⁰

Electronic Spectra

Figure 5 presents electronic spectra of the $\text{M}(\text{bqd})_2$ and $\text{M}(\text{bqd})_2\text{I}_x$ compounds as polycrystalline specimens. Data are compiled in Table VIII. Several features are noteworthy. For both nickel and palladium systems, iodination

does not produce a detectable change in the spectra at wavelengths shorter than ca. 500 nm. Considering the drastic structural change which occurs upon iodination of $\text{Ni}(\text{bqd})_2$ (monoclinic slipped stack structure with $\text{Ni-Ni} = 3.856(2)\text{\AA}$ ⁹ \rightarrow tetragonal stacked structure with $\text{Ni-Ni} = 3.153(3)\text{\AA}$ ⁸) it seems unlikely that these bands are metal-metal³ (intramolecular $\text{nd}^2 \rightarrow (n+1)\text{p}_z$ transitions with borrowing of intensity from metal \rightarrow metal charge transfer transitions³³) in origin. Rather, these are, in all likelihood, $\text{M}(\text{bqd})_2$ molecular transitions. The second noteworthy feature of the electronic spectra is the appearance of a broad transition in the 600 nm region upon iodination. We assign a major part of this absorption to the I_3^- chains. As discussed elsewhere, such intense optical transitions are typical of delocalized polyiodides.^{3,34} The spectrum of $(\text{benzamide})_2\text{H}^+\text{I}_3^-$, which is also a triiodide chain compound,³⁵ is presented in Figure 5 for comparison. A recent polarized single crystal reflectance study¹⁴ of $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$ and $\text{Pd}(\text{bqd})_2\text{I}_{0.50}$ reached the conclusion that reflectance maxima at 1.6-1.7 eV (775-730 nm)³⁶ in these materials, which were polarized in the chain direction, were metal-metal (d_z^2 band \rightarrow p_z band) in origin. Although such an assignment for the $\text{M}(\text{bqd})_2$ stacks is reasonable, it must be noted that the intense polyiodide transition should also be polarized in the chain direction.^{34c} and that the presence of the I_3^- chains cannot be ignored in such analyses.

Comparison of Metal Bisbenzoquinonedioximate Crystal Structures.

The metrical and oxidation state information contributed by the present investigation now allows a detailed assessment of the crystal structural consequences of partial oxidation. A comparison of unit cell data for the series is compiled in Table IX; bond distances and angles are set out in Table VII. In the nickel system, the unoxidized material, $\text{Ni}(\text{bqd})_2$, has a slipped-stack structure.⁹ A packing diagram, which has not previously been shown, is presented in Figure 6. As has been noted elsewhere,^{8, 13} this arrangement of the planar molecules within the unit cell allows more efficient packing (as judged by the density) than a stacked arrangement where the molecular planes are perpendicular to the stacking direction. In contrast to the $\text{Ni}(\text{bqd})_2$ result, the $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ structure is an orthorhombic stacked one. Figure 7 compares the packing of all stacked $\text{M}(\text{bqd})_2\text{I}_x$ structures. The change in crystal structure on proceeding from $\text{Ni}(\text{bqd})_2$ to $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ includes a decrease in the interplanar spacing of 0.22\AA , and a decrease in the metal-metal distance of 0.68\AA . There is no significant alteration in metrical parameters within the $\text{Ni}(\text{bqd})_2$ unit (Table VII). The crystal structure of $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ evidences large tunnels extending in the stacking direction which contain only a small amount of iodine, but which may have contained larger quantities of material at some time during the crystallization process. That polyiodide species (I_2 , I_3^- , etc.) were not detected in the resonance Raman examination of this material suggests the predominant presence of iodine as I^- and that the solid state charge distribution can be formally represented as $\text{Ni}(\text{bqd})_2^{+0.02}(\text{I}^-)_{0.02}$. The presence of undetected polyiodides (e. g. I_3^-) would mean that the degree of partial

oxidation was lower. Further oxidation of $\text{Ni}(\text{bqd})_2$ produces ' $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$ ' with iodine present predominantly as I_3^- , indicating a formal charge distribution of $\text{Ni}(\text{bqd})_2^{+0.17}(\text{I}_3^-)_{0.50/3}$. The oxidation state change is accompanied by an additional 0.027 Å contraction in the Ni-Ni distance. There is no perceptible change in the internal $\text{Ni}(\text{bqd})_2$ dimensions. Interestingly, the angle of eclipsing between $\text{Ni}(\text{bqd})_2$ units changes only slightly upon further oxidation ($68^\circ \rightarrow 65^\circ$); however, the relative orientation of the stacks changes appreciably. As can be seen in Figure 7, the effect is to provide two sets of tunnels which are nonequivalent in size and in surrounding environment. The smaller tunnel, which contains the iodine, is of approximate cross-sectional dimensions ca. $4.8 \text{ \AA} \times 4.8 \text{ \AA}$ and is lined with hydrophobic C-H residues. The larger tunnel is ca. $7.4 \text{ \AA} \times 7.4 \text{ \AA}$ in size and is surrounded by C-H groups as well as more polar oxygen atoms (which are engaged in hydrogen bonding). These tunnels contain the solvent molecules. In contrast to this result, the tunnels in $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ are all crystallographically equivalent, have both polar and non-polar regions, and differ in size ca. $5 \text{ \AA} \times 6 \text{ \AA}$ from those in $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$.

The structure of $\text{Pd}(\text{bqd})_2$ is orthorhombic with molecular planes perpendicular to the stacking direction and a 90° eclipsing angle between neighboring $\text{Pd}(\text{bqd})_2$ units (Figure 7). The degree to which this structure differs from that of monoclinic $\text{Ni}(\text{bqd})_2$ may not be energetically significant since there is evidence¹⁴ (as yet unpublished) that $\text{Pd}(\text{bqd})_2$ can also be crystallized in the same monoclinic form observed for $\text{Ni}(\text{bqd})_2$. Upon partial oxidation to $\text{Pd}(\text{bqd})_2^{+0.17}(\text{I}_3^-)_{0.50/3}$, the

Pd-Pd distance decreases by 0.019\AA and the eclipsing angle between the stacked metallomacrocycle moieties decreases by 25° . A spreading out of the lattice in the a-b plane provides tunnels for iodine and solvent inclusion. The arrangement of groups within the unit cell of $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52 \text{ o-C}_6\text{H}_4\text{Cl}_2$ is identical with that in $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$. Indeed, our refinement of the published $\text{Ni}(\text{bqd})_2\text{I}_{0.50}$ crystallographic data,⁸ reported for a crystal grown from o-dichlorobenzene,⁸ indicates residual electron density in the larger set of lattice tunnels, i. e., those which contain solvent in $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot \text{o-C}_6\text{H}_4\text{Cl}_2$. The internal structural parameters of the $\text{Pd}(\text{bqd})_2$ unit change insignificantly upon partial oxidation (Table VII).

Electrical Conductivity

Four-probe, variable temperature c-axis conductivity data for $\text{Ni}(\text{bqd})_2\text{I}_{0.50} \cdot 0.32$ toluene and $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52$ o-dichlorobenzene single crystals are shown in Figures 8 and 9, respectively. These and related data are summarized in Table X. The range of conductivities observed for the $\text{Ni}(\text{bqd})_2\text{I}_{0.50} \cdot 0.32$ toluene crystals is fairly narrow for all samples examined. The wider range for the $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52$ o- $\text{C}_6\text{H}_4\text{Cl}_2$ data includes a single sample of particularly poor conductivity. Nearly all other values were clustered at the high conductivity end of the range. Table X also compared the dc conductivity of selected $\text{M}(\text{bqd})_2\text{I}_{0.50} \cdot \text{S}$ crystals with measurements at a frequency of 100 Hz. For $\text{M} = \text{Pd}$, there is good agreement between the techniques. For $\text{M} = \text{Ni}$, there is less good agreement, which is attributed to the integrity of the electrode contacts. The nickel-containing specimens presented the greatest measurement

difficulties, and a large number of crystals were rejected owing to fractures and to non-ohmic electrode behavior.

It can be seen in Table X that the conductivities of the uniodinated $M(bqd)_2$ materials are immeasurably low. As has been observed for the metal bisdiphenylglyoximates and similar macrocycles, partial oxidation such as to $M(bqd)_2^{+0.17}$ results in a large increase in electrical conductivity. The enhancement for the bisbenzoquinonedioximates is ca. $10^3 - 10^6$. Interestingly, considerably lower conductivities are observed for the $Ni(bqd)_2I_{0.02}$ crystals than for the $Ni(bqd)_2I_{0.32}$ toluene crystals. This may reflect the differences in crystal structure as well as the decreased number of charge carriers generated by the smaller degree of partial oxidation. In the only other case to date where it has been possible to vary the apparent degree of metallomacrocycle oxidation, i. e., $Ni(OMTBP)I_x$, OMTBP = 1,4,5,8,9,12,13,16-octamethyltetrabenzoporphyrin, $x = 1.05(1)$ and $2.9(3)$ (iodine present as I_3^-),³⁷ the $x = 2.9$ materials appear to be slightly less conductive. The difference is not nearly so large as in the present case.

The dc conductivities of the $M(bqd)_2I_{0.30}$ S materials obey eq. (2)

$$\sigma = \sigma_0 e^{-\Delta/kT} \quad (2)$$

over the range of temperatures shown in Figures 8 and 9. The $M(dpg)_2I$ compounds exhibit similar behavior.³ At the highest temperatures some $M(bqd)_2I_{0.30}$ S samples did display a tendency toward levelling-off in the $\ln \sigma$ vs. $1/T$ plot. Efforts to confirm "metal-like" behavior, i. e., decreasing conductivity with increasing temperature, by acquiring additional data at even higher

temperatures, resulted in irreversible sample decomposition. Table X contains apparent activation energies, Δ , obtained by a least-squares fit to eq. (2).

The range indicated represents the largest deviation from the average for the samples plotted. As was noted in the discussion of the $M(\text{dpg})_2\text{I}$ conductivity data,³ the thermally activated temperature dependence of charge transport in these materials is consistent with either of two theoretical descriptions: phonon-assisted carrier hopping between states localized by static disorder,³⁸ or an activated carrier concentration in a system with a Mott-Hubbard or some other type of gap.³⁹ For the former model, the disorder in the I_3^- chains would presumably be the source of the disorder, while for the latter model, the classical Mott-Hubbard gap^{38d, 39b} is inappropriate for the $M(\text{bqd})_2\text{I}_{0.50}\text{S}$ bands, which are ca. 92% filled.

Table X also compares the $M(\text{bqd})_2\text{I}_{0.5}\text{S}$ conductivity data with those for $M(\text{dpg})_2\text{I}$ materials. Even after adjusting the transport behavior for crystal structure by using the carrier mean free path (eq. (3)), it can be

$$L = \frac{\pi \hbar A \sigma}{2e^2 N} \quad (3)$$

seen that the bisbenzoquinonedioximate materials are less conductive.

Apparent activation energies are, however, more comparable (Table X), and in each bisglyoximate series the Δ values for the highest conductor and lowest conductor are similar.

CONCLUSIONS

The results of the present investigation indicate that the $M(bqd)_2I_{0.50}$ materials, $M = Ni, Pd$, are best formulated as $M(bqd)_2I_{0.50} \cdot S$ materials where S represents various amounts of the aromatic solvent employed for crystallization. As deduced from resonance Raman, I-129 Mössbauer, and diffuse x-ray scattering measurements,¹⁵ the iodine is present as I_3^- , and thus the $M(bqd)_2I_{0.50} \cdot S$ materials are indeed partially oxidized. The formal fractional oxidation state of the $M(bqd)_2$ units is +0.17. Based upon estimated uncertainties in stoichiometry and I_3^- content we assign to this oxidation state an uncertainty of 0.02 charge units. It is interesting to note that the degree of charge transferred in the present case is identical within experimental error, to that deduced in the bisdiphenylglyoximate materials, $M(dpg)_2I$, $M = Ni, Pd$. Here iodine was present predominantly as I_3^- so that the formal oxidation state of each $M(dpg)_2$ moiety was +0.20(4).³

In both benzoquinonedioximate and diphenylglyoximate systems, partial oxidation is accompanied by contraction in the interplanar stacking distances. The shortest metal-metal distance observed for a stacked, partially oxidized metal bisdioximate is 3.153(3) Å in $Ni(bqd)_2I_{0.50}$,⁸ with the distance in $Pd(bqd)_2I_{0.50} \cdot 0.52$ o-dichlorobenzene being only slightly longer, i. e., 3.184(3) Å. Contacts in the $M(dpg)_2I$ species are somewhat longer with $Ni-Ni = 3.271(1)$ Å and $Pd-Pd = 3.25$ Å.³ These metal-metal distances are greater than in $K_2Pt(CN)_4Br_{0.50}$ (2.89 Å)^{4,40} as well as in the integral oxidation state face-to-face metallomacrocycle dimers $[Ni(C_{14}H_{13}N_4)]_2^{+2}$ (A, $Ni-Ni = 3.063(1)$ Å)²⁷ and $[Ni(C_{15}H_{14}N_5)]_2$ (B, $Ni-Ni = 2.788(2)$).²⁸ However, since the nickel atoms

in the latter two compounds are significantly displaced from the ligand planes⁴¹ (and toward each other) it is more meaningful to discuss the interplanar spacing. This value for A is 3.19 Å, and for B is 3.00 Å, which is in better agreement with the stacked bisdioximate parameters. The attractive forces in the face-to-face dimers are considered to involve both metal-metal σ and δ bonding as well as ligand-ligand π bonding.^{27, 28} It is likely that similar effects are operative in the stacked bisdioximates, with the result of partial oxidation being to depopulate orbitals (bands) which are metal-metal (e. g. nd_{z^2} ⁴²) or ligand-ligand antibonding⁴³ in character. The lengths of the Ni-Ni and Pd-Pd contacts as well as the relative insensitivity of the stacking distances to metal identity suggests that the metal-metal bonding is rather weak. That the interactions do not persist in solution indicates that the overall attractive forces are not very great. As a point of reference, the interplanar spacing in Ni(Pc)I is 3.244(3) Å,^{5f} in graphite is 3.35 Å,⁴⁴ and in the TCNQ stacks of typical organic conductors is 3.17-3.30 Å.⁴⁵ In the absence of some attractive forces, distances in the 3.0 Å range are considered to be moderately repulsive.⁴⁶

Partial oxidation of the $M(bqd)_2$ and $M(dpg)_2$ materials to the 0.17-0.20 formal oxidation state results in an electrical conductivity increase of $10^3 - 10^8$ in the molecular stacking direction. For $Ni(bqd)_2I_{0.88}$, the small degree of oxidation results in a greatly diminished electrical conductivity. For the partially oxidized $M(bqd)_2$ and $M(dpg)_2$ materials, there is no clear-cut dependence of the charge transport facility on metal or interplanar spacing. The approximate order of conductivity is

$\text{Ni(dpg)}_2\text{I} > \text{Pd(dpg)}_2\text{I} \approx \text{Pd(bqd)}_2\text{I}_{0.50}\cdot\text{S} > \text{Ni(bqd)}_2\text{I}_{0.50}\cdot\text{S}$. There is no evidence in the present case that the chains of metal atoms provide the major conductive pathway, and judging from results on macrocyclic systems (phthalocyanine,^{5b} dibenzotetraazaannulene^{5e}) where both metal and metal-free species are conductive when partially oxidized, it is likely that the ligand (i.e., molecular orbitals which are largely ligand in character) plays an important if not predominant role in the conductivity of the bisdioximate materials. The temperature dependence of the conductivity in the present materials is thermally activated with slight, if any, onset of "metal-like" behavior at highest temperatures. The functional dependence is reminiscent of "intermediate conductivity" TCNQ salts,^{45b} and is consistent with phonon-assisted hopping of the carriers between states localized by disorder,³⁸ or with a weakly localized system having a gap and a temperature-dependent carrier concentration.³⁹

ACKNOWLEDGMENTS

This work was generously supported under the NSF-MRL program through the Materials Research Center of Northwestern University (grant DMR76-80847), by the Office of Naval Research (grant N00014-77-C-0231 to T. J. M.), the Department of Energy (S. L. R.), and the National Science Foundation (grant CHE76-10335 to J. A. I.).

Supplementary material available: A listing of structure amplitudes (pp)

Ordering information is given on any current masthead page.

References

- (1) a. Department of Chemistry, Northwestern University
b. Department of Electrical Engineering, Northwestern University
- (2) a. Fellow of the Alfred P. Sloan Foundation.
b. Camille and Henry Dreyfus Teacher-Scholar
- (3) Cowie, M.A.; Gleizes, A.; Grynkewich, G.W.; Kalina, D.W.; McClure, M.S.; Scaringe, R. P.; Teitelbaum, R. C.; Ruby, S. L.; Ibers, J.A.; Kannewurf, C.R.; Marks, T.J. previous article.
- (4) a. Miller, J.S.; Epstein, A.J. Prog Inorg. Chem., 1976, 20, 1-152.
b. Zeller, H.R. "Low-Dimensional Cooperative Phenomena," Keller, H.J. ed., Plenum Press, N.Y., 1975, p. 215-233.
- (5) a. Marks, T.J. Ann. N.Y. Acad. Soc., in press.
b. Petersen, J.L.; Schramm, C.S.; Stojakovic, D.R.; Hoffman, B.M.; Marks, T.J. J. Amer. Chem. Soc. 1977, 99, 286-288.
c. Marks, T.J.; Lin, L. -S., manuscript in preparation.
d. Marks, T.J.; Kundalkar, B., manuscript in preparation.
e. Schramm, C. S.; Stojakovic, D.R.; Hoffman, B.M.; Marks, T. J. Science, 1978, 200, 47-48.
f. Peterson, J.L.; Schramm, C.S.; Scaringe, R. P.; Stojakovic, D.R.; Hoffman, B.; Ibers, J.A.; Marks, T.J. manuscript in preparation.
- (6) Burger, K.; Ruff, I. Acta. Chim. Acad. Sci. Hung., 1966, 49, 1-9.
- (7) Endres, H.; Keller, H.J.; Megnamisi-Bélombé, M.; Moroni, W.; Nöthe, D. Inorg. Nucl. Chem. Letters, 1974, 10, 467-471.
- (8) Endres, H.; Keller, H.J.; Moroni, W.; Weiss, J. Acta. Cryst., 1975, B31, 2357-2358.
- (9) Leichert, I.; Weiss J. Acta. Cryst., 1975, B31, 2877-2878.
- (10) Leichert, I.; Weiss, J. Acta. Cryst., 1975, B31, 2709-2710.
- (11) In reference 7, preliminary conductivity measurements were reported using silver paste electrical contacts. A time-dependent decrease in the conductivity was taken as evidence that the iodinated materials were reacting with the silver contacts.
- (12) Marks, T.J.; Webster, D.F.; Ruby, S. L.; Schultz, S. J. Chem. Soc. Chem. Comm., 1976, 444-445.
- (13) Endres, H.; Keller, H.J.; Megnamisi-Bélombé, M.; Moroni, W.; Pritzkow, H.; Weiss, J.; Comes, R. Acta. Cryst., 1976, A32, 954-957.

- (14) Brill, J.W.; Megnamisi-Bélombé, M.; Novotny, M. J. Chem. Phys., 1978, 68, 585-592.
- (15) Boyer, J.H.; Ellzey, S.E. J. Amer. Chem. Soc., 1960, 82, 2525-2528.
- (16) a. Cornu, A.; Massot, R. Compilation of Mass Spectral Data, 1968, Heyden and Son, Ltd., London, p. 28c.
b. Mass Spectral Data, American Petroleum Institute Research Project 144, 1948, p. 251.
- (17) See, for example, Waters, J.M.; Ibers, J.A. Inorg. Chem., 1977, 16, 3273-3277.
- (18) See paragraph at end of paper regarding supplementary material.
- (19) a. Teitelbaum, R.C.; Ruby, S.L.; Marks, T.J. J. Amer. Chem. Soc., 1978, 100, 3215-3277.
b. Kalina, D.W.; Stojakovic, D.R.; Teitelbaum, R.C.; Marks, T.J., manuscript in preparation.
- (20) a. Kiefer, W. Appl. Spectrosc., 1974, 28, 115-134.
b. Trotter, P.J.; White, P.A. Appl. Spectrosc., 1978, 32, 323-324.
- (21) a. Herbstein, F.H.; Kapon, M. Nature (London), 1972, 239, 153-154.
b. Havinga, E.E.; Boswijk, K.H.; Wiebenga, E.H. Acta. Cryst., 1954, 7, 487-490.
c. Havinga, E.E.; Wiebenga, E.H. Acta. Cryst., 1958, 11, 733-737.
- (22) a. Gibb, T.C., "Principles of Mössbauer Spectroscopy," Chapman and Hall, London, 1976, Chapt. 4.2.
b. Bancroft, G.M.; Platt, R.H. Adv. Inorg. Chem. Radiochem., 1972, 15, 187-201.
- (23) The staggering angle in the structures of $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ and $\text{Pd}(\text{bqd})_2\text{I}_{0.50}$ 0.52 $\text{o-C}_6\text{H}_4\text{Cl}_2$ is the calculated dihedral angle between the M-N(1) bond of an $\text{M}(\text{bqd})_2$ moiety and the M-N(2)' bond of a nearest neighbor $\text{M}(\text{bqd})_2$ unit along the stacking axis.
- (24) Robertson, J.M.; Woodward, I. J. Chem. Soc., 1937, 219-230.
- (25) Banks, C.V.; Barnum, D.W. J. Amer. Chem. Soc., 1958, 80, 4767-4772.
- (26) Williams, D.E.; Wohlaue, G.; Rundle, R.E. J. Amer. Chem. Soc., 1959, 81, 755-756.
- (27) Peng, S.-M.; Ibers, J.A.; Millar, M.; Holm, R.H., J. Amer. Chem. Soc., 1976, 98, 8037-8041.
- (28) Peng, S.-M.; Goedken, V.L., J. Amer. Chem. Soc., 1976, 98, 8500-8510.
- (29) Handbook of Chemistry and Physics, 57th ed., Chemical Rubber Publishing Co., Cleveland, Ohio, 1976-1977, F-216.

- (30) Endres, H.; Keller, H.J.; Lehmann, R.; Weiss, J. Acta. Cryst., 1976, B32, 627-628.
- (31) a. Miller, J.S.; Griffiths, C.H. J. Amer. Chem. Soc., 1977, 99, 749-755.
 b. Foust, A.S.; Soderberg, R. J. Amer. Chem. Soc., 1967, 89, 5507-5508.
 c. Miller, J.S.; Goldberg, S.Z. Inorg. Chem., 1975, 14, 2294-2296.
- (32) Calleri, M.; Ferraris, G.; Viterbo, D. Inorg. Chim. Acta., 1967, 1, 297-302.
- (33) a. Hara, Y.; Shirotani, I.; Onodera, A. Solid State Comm., 1976, 19, 171-175.
 b. Anex, B.G., A.C.S. Symposium Series, 1974, 5, 276-300.
 c. Ohashi, Y.; Hanazaki, I.; Nagakura, S. Inorg. Chem., 1970, 9, 2551-2556.
- (34) a. Stojakovic, D.R., Ph.D. Thesis, Northwestern University, Evanston, Illinois, August 1977.
 b. Gabes, W.; Stufkens, D.J. Spectrochim. Acta, 1974, 30A, 1835-1841.
 c. Robin, M.B. J. Chem. Phys., 1964, 40, 3369-3377.
- (35) Reddy, J.M.; Knox, K.; Robin, M.B. J. Chem. Phys., 1964, 40, 1082-1089.
- (36) Without a Kramer-Kronig analysis of the reflectance data,^{33b} the spectral maxima cannot be precisely related to the absorption maxima.
- (37) a. Phillips, T.E.; Hoffman, B.M. J. Amer. Chem. Soc., 1977, 99, 7734-7736
 b. Scaringe, R.P.; Phillips, T.E.; Hoffman, B.M.; Ibers, J.A., unpublished results.
- (38) a. Shante, V.K.S. Phys. Rev. B., 1977, 16, 2597-2612, and references therein.
 b. Cohen, M.H. Lecture Notes in Physics, 1977, 65, 225-262, and references therein.
 c. Mihaly, G.; Ritvay-Emandity, K.; Janossy, A.; Holczer, K.; Gruner, G. Solid State Comm., 1977, 21, 721-724.
 d. Mott, N.F., Metal-Insulator Transitions, Taylor and Francis, London, 1974, chapt. 1.
- (39) a. Epstein, A.J.; Conwell, E.M.; Sandman, D.J.; Miller, J.S. Solid State Comm., 1977, 23, 335-358.
 b. Epstein, A.J.; Conwell, E.M. Solid State Comm., 1977, 24, 627-630.
 c. Conwell, E.M. Phys. Rev. Lett., 1977, 39, 777-780.

- (40) Williams, J.M.; Petersen, J.L.; Gerdes, H.M.; Peterson, S.W. Phys. Rev. Lett., **1974**, *33*, 1079-1081.
- (41) That is, the least squares plane defined by the four coordinated nitrogen atoms.²⁷
- (42) a. Interrante, L.V.; Messmer, R.P. Advan. Chem. Ser., **1975**, *5* 382-391.
b. Messmer, R.P.; Salahub, D.R. Phys. Rev. Lett., **1975**, *35*, 533-536
- (43) Miller, J.S. Inorg. Chem., **1977**, *16*, 957-960, and references therein
- (44) Cotton, R.A.; Wilkinson, G. Advanced Inorganic Chemistry, 3rd Ed., Wiley-Interscience, N.Y., 1972, p 288.
- (45) a. Cowan, D.; Shu, P.; Hu, C.; Krug, W.; Carruthers, T.; Poehler, T.; Block, A. in Chemistry and Physics of One-Dimensional Metals, Keller, H.J., Ed., Plenum Press, N.Y., 1977, p. 25-47.
b. Herbstein, F.H. Perspectives in Structural Chemistry, Dunitz, J.D.; Ibers, U.A., Eds., Wiley, N.Y., 1971, Vol. IV, p. 344.
c. Shchegolev, I.F. Phys. State. Sol(a), **1972**, *12*, 9-45.
- (46) Williams, J.; Stang, P.; Schleyer, P. Ann. Rev. Phys. Chem., **1968**, *19*, 531-558.

Table I

Crystal Data and Details of Data Collection and Structure Refinement

Compound	Ni(bqd) ₂ I _{0.02}	Pd(bqd) ₂ I _{0.48} (C ₆ H ₄ Cl ₂) _{0.91}
Formula	C ₁₂ H ₁₀ I _{0.02} N ₄ NiO ₄	C _{17.48} H _{13.64} Cl _{1.82} I _{0.478} N ₄ O ₄ Pd
Formula weight, amu	355.19	575.07
a, Å	16.438(5)	16.048(7)
b, Å	14.759(4)	16.048(7)
c, Å	6.360(2)	6.367(3)
V, Å ³	1543.2	1639.6
Space Group	D _{2h} ²⁶ - Ibam	D _{4h} ² - P4/mcc
Z	4	4
ρ _{calc} , g/cm ³	1.443	2.320
Radiation	CuKα	MoKα
Crystal shape	{001}{110} faces, needle axis [001]	{001}{110} faces, needle axis [001]
Crystal dimensions, mm	0.8 x 0.1 x 0.1	0.8 x 0.2 x 0.2
Crystal volume, mm ³	0.0062	0.030
μ, cm ⁻¹	21.9	23.4
Transmission factors	0.703 to 0.864	0.619 to 0.697
Takeoff angle, deg	4.2	2.5
Aperture, mm	5.5 x 4.8 32 cm from x1	4.0 x 4.8 32 cm from x1
Scan speed, deg/min	2.0	2.0

Scan range, deg	0.85 below $K\alpha_1$ to 0.85 above $K\alpha_2$	0.85 below $K\alpha_1$ to 0.85 above $K\alpha_2$
Background counting times	20 sec with rescan option	20 sec with rescan option
2 θ range	3 to 160°	3 to 80°
Data collected	$h, k, \pm l$	$h \geq k, l$ with l odd terminated at 55° $h \neq k, -l$ to 40°
p	0.04	0.03
Unique data with $F_o^2 > 3\sigma(F_o^2)$	1026	1278
Number of variables	65	74
R index	0.11	0.052

40

Table II. Positional and Thermal Parameters for the Atoms of $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$

ATOM	x	y	z	011 ^a OR 0.1 ²	022	033	012	013	023
Ni	0	0	0	4.09(11)	4.33(12)	22.06(79)	0.13(12)	0	0
O(1)	0.16497(63)	-0.09610(71)	0	5.46(66)	9.31(60)	32.6(30)	3.23(60)	1	0
O(2)	-0.02745(66)	0.10933(66)	0	5.07(60)	6.02(49)	30.1(34)	2.00(64)	0	0
N(1)	0.11201(62)	-0.01692(64)	0	3.46(33)	6.71(69)	25.6(29)	0.73(36)	0	0
N(2)	0.02939(93)	0.12475(74)	0	0.65(69)	6.79(59)	23.6(31)	-0.07(60)	0	0
C(1)	0.15476(63)	0.0605(11)	0	4.33(50)	10.9(11)	17.2(64)	-1.11(66)	0	0
C(2)	0.1005(10)	0.1430(10)	0	5.17(66)	6.91(75)	17.5(60)	-2.03(67)	0	0
C(3)	0.1623(15)	0.2207(13)	0	10.6(13)	7.0(11)	39.9(69)	-2.0(20)	0	1
C(4)	0.2275(23)	0.2243(20)	0	14.6(19)	25.5(32)	27.7(57)	-1.0(11)	0	0
C(5)	0.2001(15)	0.1446(29)	0	5.4(12)	20.0(17)	61.5(60)	-0.9(16)	0	0
C(6)	0.2407(11)	0.0643(19)	0	5.66(70)	10.9(11)	29.9(69)	-1.7(16)	0	0
NIC(3)	0.112	0.200	0	9.4					
NIC(4)	0.253	0.206	0	14.9					
NIC(5)	0.330	0.155	0	13.0					
NIC(6)	0.203	0.009	0	14.1					

^a ESTIMATE. STANDARD DEVIATIONS IN THE LEAST SIGNIFICANT FIGURE(S) ARE GIVEN IN PARENTHESES IN THIS AND ALL SUBSEQUENT TABLES. ^b THE FORM OF THE ANISOTROPIC THERMAL ELLIPSOID IS: $E^{-2} = (h^2/0.011 + 0.22h + 0.33l + 20.12hk + 26.13hl + 20.23kl)$. THE QUANTITIES GIVEN IN THE TABLE ARE THE THERMAL COEFFICIENTS $\times 10^3$.

Table IV. Positional and Thermal Parameters for the Atoms of $\text{Pd}(\text{bqd})_2\text{I}_{0.48}\cdot 0.91$
o-dichlorobenzene.

ATOM	x	y	z	011 OR 01A ²	022	033	012	013	023
I	1/2	1/2	1/4	5.64(5)	5.64	54.53(63)	0	0	0
Pd	0	1/2	0	3.83(3)	3.65(3)	15.44(14)	0.48(4)	0	0
O(1)	0.15750(34)	0.40910(34)	0	4.66(26)	4.81(27)	39.5(18)	1.79(23)	0	0
O(2)	0.90204(37)	0.60220(35)	0	7.38(38)	3.95(23)	35.6(19)	1.48(23)	0	0
N(1)	0.12319(41)	0.48204(41)	0	4.25(27)	5.74(40)	16.5(15)	0.76(23)	0	0
N(2)	0.03502(44)	0.61647(40)	0	5.32(31)	4.09(20)	18.0(17)	0.14(24)	0	0
C(1)	0.16713(54)	0.55317(53)	0	5.19(41)	5.49(43)	14.0(17)	-0.50(36)	0	0
C(2)	0.11747(54)	0.62095(52)	0	5.57(41)	4.06(38)	18.0(18)	-0.51(33)	0	0
C(3)	0.15949(69)	0.70790(62)	0	8.62(64)	5.69(49)	29.1(30)	-2.12(45)	0	0
C(4)	0.24404(83)	0.70553(92)	0	8.04(77)	9.22(75)	30.4(33)	-5.12(59)	0	0
C(5)	0.29217(64)	0.63317(96)	0	4.97(49)	12.34(92)	34.9(37)	-2.90(57)	0	0
C(6)	0.25675(53)	0.55806(75)	0	3.93(37)	9.49(64)	25.7(25)	-1.08(40)	0	0
H(3)	0.134	0.762	0	6.0					
H(4)	0.274	0.757	0	7.9					
H(5)	0.352	0.644	0	8.0					
H(6)	0.291	0.508	0	6.1					
H(10-O)	0.088	0.364	0	6.0					
CL	0.04050(96)	0.12534(77)	0.1431(18)	27.86(66)					

^A ESTIMATED STANDARD DEVIATIONS IN THE LEAST SIGNIFICANT FIGURE(S) ARE GIVEN IN PARENTHESES IN THIS AND ALL SUBSEQUENT TABLES. ^B THE FORM OF THE ANISOTROPIC THERMAL ELLIPSOID IS: $\text{EXP}[-(\text{B}11\text{H}^2 + \text{B}22\text{K}^2 + \text{B}33\text{L}^2 + 2\text{B}12\text{HK} + 2\text{B}13\text{HL} + 2\text{B}23\text{KL})]$. THE QUANTITIES GIVEN IN THE TABLE ARE THE THERMAL COEFFICIENTS $\times 10^3$.

TABLE VI. Raman Data for Metal Bisbenzoquinonedioximates.^{a,b}

Ni(bqd)₂: none detected

Ni(bqd)₂I_{0.02}: none detected

Ni(bqd)₂I_{0.52}·0.32 toluene: 322w, 215w, 153w, 107s

Pd(bqd)₂: none detected

Pd(bqd)₂I_{0.5}·0.52 o-C₆H₄Cl₂: 322w, 215m, 155w, 107s

^aPolycrystalline samples, 5145Å excitation

^bIn cm⁻¹; s = strong, m = medium, w = weak

TABLE VII. Comparison of Bond Distances and Angles in Nickel and Palladium Bisbenzoquinonedioximates.^a

M-M	Ni(bqd) ₂ I ₀ . ^b	Ni(bqd) ₂ I ₀ . ^c	Ni(bqd) ₂ . ^d	Pd(bqd) ₂ I ₀ . ^e	Pd(bqd) ₂ . ^f
M-N(1)	3.180(1)Å	3.153(3)Å	3.856(2)Å	3.183(2)Å	3.202Å
N(1)-N(2)	1.858(10)	1.91(2)	1.868(4)	1.996(7)	2.00(2)
N(1)-O(1)	1.904(10)	1.90(2)	1.860(5)	1.955(7)	1.95(2)
N(2)-O(2)	1.288(12)	1.33(3)	1.313(7)	1.305(7)	1.34(2)
N(1)-C(1)	1.335(16)	1.28(3)	1.313(8)	1.356(8)	1.33(3)
N(2)-C(2)	1.341(17)	1.27(4)	1.309(8)	1.331(10)	1.29(3)
C(1)-C(2)	1.199(20)	1.35(4)	1.313(8)	1.325(10)	1.35(3)
C(1)-C(6)	1.510(22)	1.50(4)	1.445(8)	1.454(11)	1.47(3)
C(2)-C(3)	1.545(20)	1.44(4)	1.424(8)	1.441(12)	1.43(3)
C(3)-C(4)	1.440(21)	1.42(4)	1.427(9)	1.435(12)	1.43(3)
C(4)-C(5)	1.402(46)	1.42(6)	1.346(10)	1.358(15)	1.38(4)
C(5)-C(6)	1.460(45)	1.42(7)	1.432(11)	1.395(18)	1.48(4) ³⁷
O(1)-O(2)	1.297(38)	1.32(6)	1.338(11)	1.333(15)	1.34(4)
	2.372(17)	2.43(3)	2.480(6)	2.687(9)	2.66(4)
N(1)-M-N(2)	83.0(5)°	84(1)°	83.6(2)°	80.8(3)°	81(1)°
O(1)-N(1)-C(1)	123.5(11)	122(2)	124.9(4)	123.0(7)	124
O(2)-N(2)-C(2)	121.4(14)	122(2)	125.7(4)	120.1(7)	120
C(1)-C(2)-C(3)	115.2(16)	122(3)	119.11(5)	118.7(8)	121(2)
C(2)-C(3)-C(4)	129.0(23)	112(2)	118.6(6)	116.4(11)	119(2)
C(3)-C(4)-C(5)	120.2(23)	129(4)	122.1(7)	125.2(11)	120(3)
C(4)-C(5)-C(6)	115.4(25)	120(4)	121.5(7)	121.1(10)	123(3)
C(5)-C(6)-C(1)	124.3(16)	119(3)	117.0(6)	118.4(10)	120(2)
C(6)-C(1)-C(2)	113.9(9)	119(3)	119.8(6)	120.1(8)	117(2)

TABLE VII continued

M-N(1)-C(1)	113.9(9)	115(2)	114.	114.0(6)	122(1)
M-N(2)-C(2)	117.7(12)	113(2)	114.	115.8(6)	124(1)

^a Atom numbering scheme is that in Figure 3.

^b This work.

^c Reference 8 and the refinement described in this work.

^d Reference 9.

^e This work.

^f Reference 10

TABLE VIII. Electronic Spectral Data for Metal Bisbenzoquinonedioximates in nm(kK).

Compound	Nujol mull		CHCl ₃ solution	
Ni(bqd) ₂	238	(42.0)		
	318	(31.4)	308	(32.5)
	420sh	(23.8)	417	(24.0)
	472	(21.2)	455	(22.0)
	590	(16.9)	553sh	(18.1)
Ni(bqd) ₂ I _{0.52} · 0.32 toluene	220sh	(45.5)		
	260	(38.5)		
	315	(31.7)		
	450	(22.2)		
	540	(18.5)		
	650br	(15.4)		
	802	(12.5)		
Pd(bqd) ₂	235	(42.6)		
	295sh	(33.9)		
	325sh	(30.8)	335	(29.8)
	385	(26.0)	393	(25.4)
	440sh	(22.7)	505sh	(19.8)
	680	(14.7)	650br	(15.4)
Pd(bqd) ₂ I _{0.50} · 0.52 <u>o</u> -C ₆ H ₄ Cl ₂	295sh	(33.9)		
	320sh	(31.2)		
	390	(25.6)		
	440sh	(22.7)		
	605sh	(16.5)		
	685br	(14.6)		

^a sh = shoulder, br = broad.

TABLE IX. Comparison of Unit Cell Parameters for Various Metal Benzoquinonedioximates

	a	b	c	d	
Compound	Ni(bqd) ₂	Ni(bqd) ₂ I _{0.02}	Ni(bqd) ₂ I _{0.50}	Pd(bqd) ₂	Pd(bqd) ₂ I _{0.47}
Space Group	C _{2h} ⁵ -P2 ₁ /n	D _{2h} ²⁶ -Ibam	D _{4h} ² -P4/mcc	D _{2h} ²⁶ -Imcb	D _{4h} ² -P4/mcc
Z	2	4	4	4	4
a, Å	3.856(3)	16.438(2)	15.553(4)	6.405(1)	16.048(7)
b, Å	9.461(6)	14.759(4)	15.553(4)	9.728(1)	16.048(7)
c, Å	16.542(12)	6.360(2)	6.307(3)	20.649(2)	6.367(3)
β, deg	90.45(6)	90	90	90	90
V, Å ³	603.5	1543.2	1525.6	1286	1639.6
Symmetry imposed on M(bqd) ₂	$\bar{1}$	2/m	2/m	2/m	2/m

^aReference 9^bThis work^cReference 8^dReference 10.

TABLE X. Single Crystal (c axis) Electrical Conductivity

Data for Metal Bisbenzoquinonedi oximates and Bisdiphenylglyoximates

Material	dc Conductivity ^c at 300°K (Ω-cm) ⁻¹	Conductivity Comparison at 300°K (Ω-cm) ⁻¹ dc	Δ(eV) ^f ac (100Hz)	L(Å) ^g
Ni(bqd) ₂	< 9 x 10 ⁻⁹			< 7.0 x 10 ⁻¹³
Ni(bqd) ₂ I _{0.03}	< 9 x 10 ⁻⁹			
Ni(bqd) ₂ I _{0.03} · S ^a	1.8 - 11 x 10 ⁻⁶	1.8 x 10 ⁻⁶	1.1 x 10 ⁻⁷	0.54 ± 0.08
Pd(bqd) ₂	< 2 x 10 ⁻⁹			
Pd(bqd) ₂ I _{0.03} · S ^b	7.8-810 x 10 ⁻⁵	5.6 x 10 ⁻³	4.5 x 10 ⁻⁸	0.22 ± 0.03
Ni(dpg) ₂ I	2.3 - 11 x 10 ⁻²			0.19 ± 0.01
Pd(dpg) ₂ I	7.7 - 47 x 10 ⁻⁴			0.54 ± 0.11
				4.0-20 x 10 ⁻⁴ d
				1.3-8.0 x 10 ⁻⁶ d

^aS = 0.32 toluene

^bS = 0.52 o-dichlorobenzene

^cRange for crystals examined

^dFrom reference 3.


^eData for the same crystal

^fFrom least-squares fit to the equation $\sigma = \sigma_0 e^{-\Delta k T}$


^gFrom the relationship $L = \frac{\pi \hbar A \sigma}{2e^2 N}$

Figure 1. Resonance Raman spectra ($\nu_0 = 5145\text{\AA}$) of A. $\text{Pd}(\text{bqd})_2\text{I}_{0.5} \cdot 0.52$ o-dichlorobenzene, B. $\text{Pd}(\text{bqd})_2$, C. $\text{Ni}(\text{bqd})_2\text{I}_{0.52} \cdot 0.32$ toluene, D. $\text{Ni}(\text{bqd})_2$. Weak transitions in B. and D. at 117 and 77 cm^{-1} result from laser plasma emission.


A

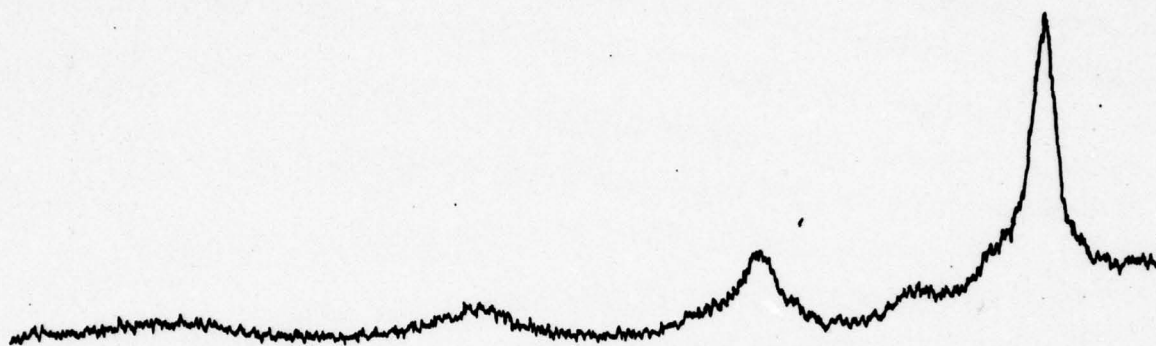


B



C

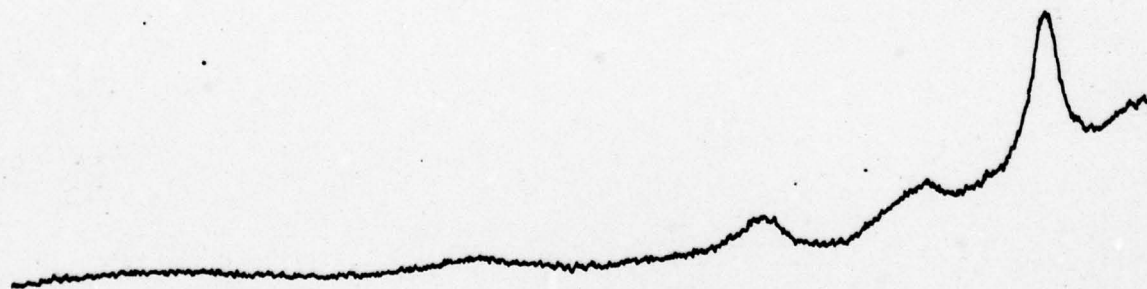

D

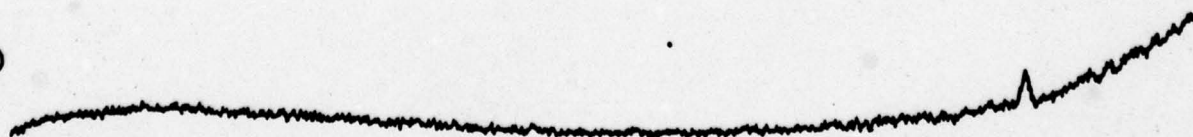

500

400

300

200

100

WAVENUMBER (cm⁻¹)

Figure 2. View of the unit cell of $\text{Ni}(\text{bqd})_2\text{I}_{0.02}$ along the stacking direction. The \underline{a} -axis is vertical from bottom to top, the \underline{b} -axis is horizontal to the right, and the \underline{c} -axis is towards the reader. The vibrational ellipsoids are drawn at the 50% level.

Top

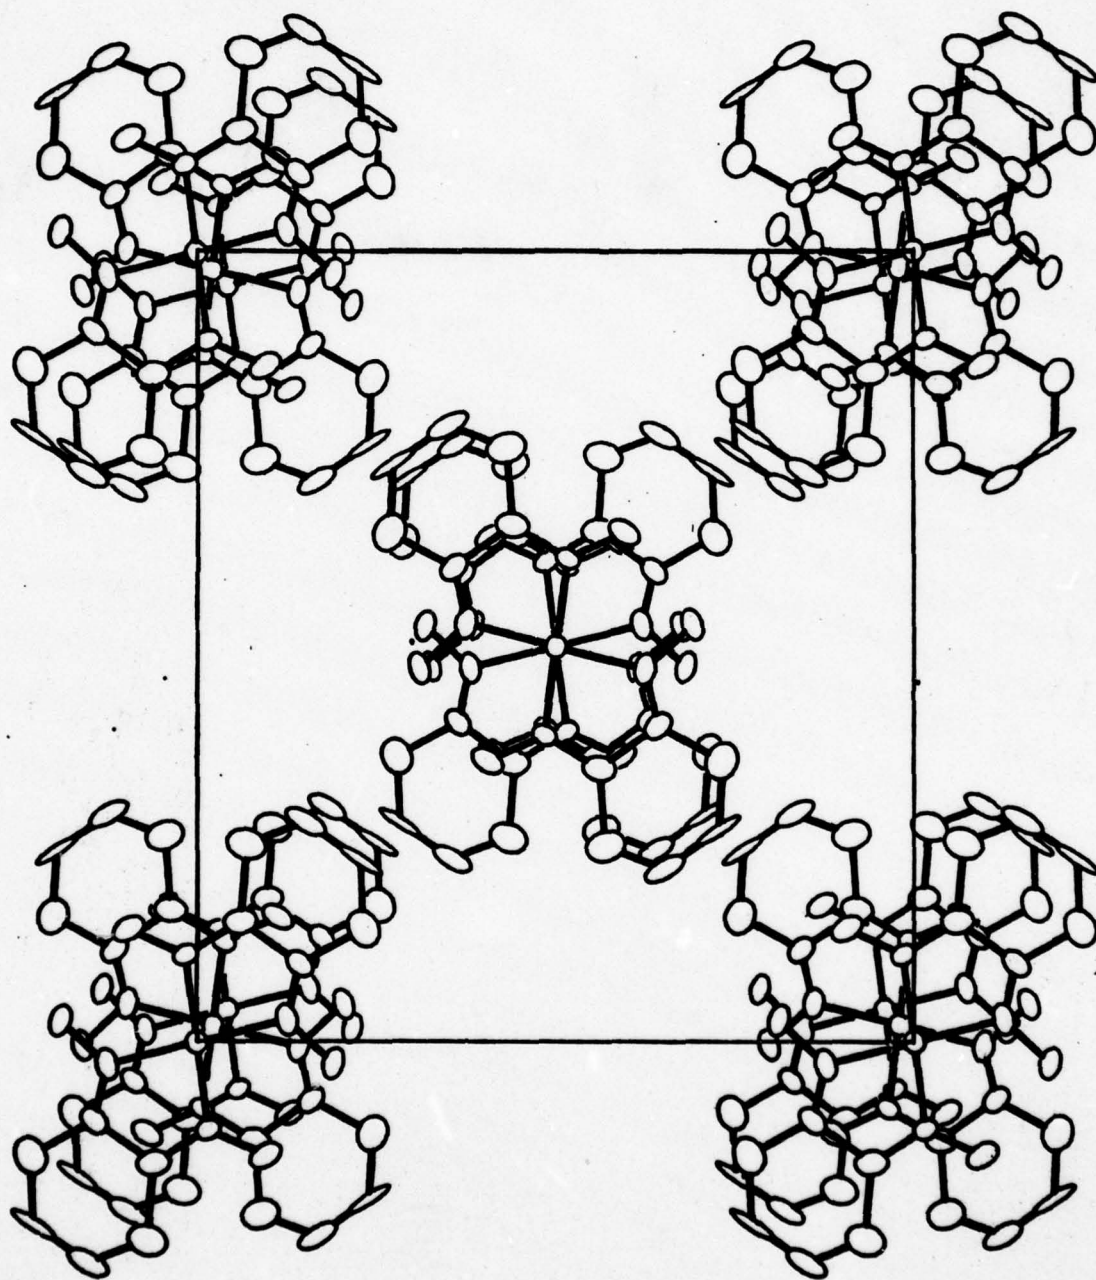


Figure 3. A drawing of the $\text{Ni}(\text{bqd})_2$ molecule in $\text{Ni}(\text{bqd})_2 \cdot \text{I}_{0.02}$ showing the atom numbering scheme. The vibrational ellipsoids are drawn at the 50% level.

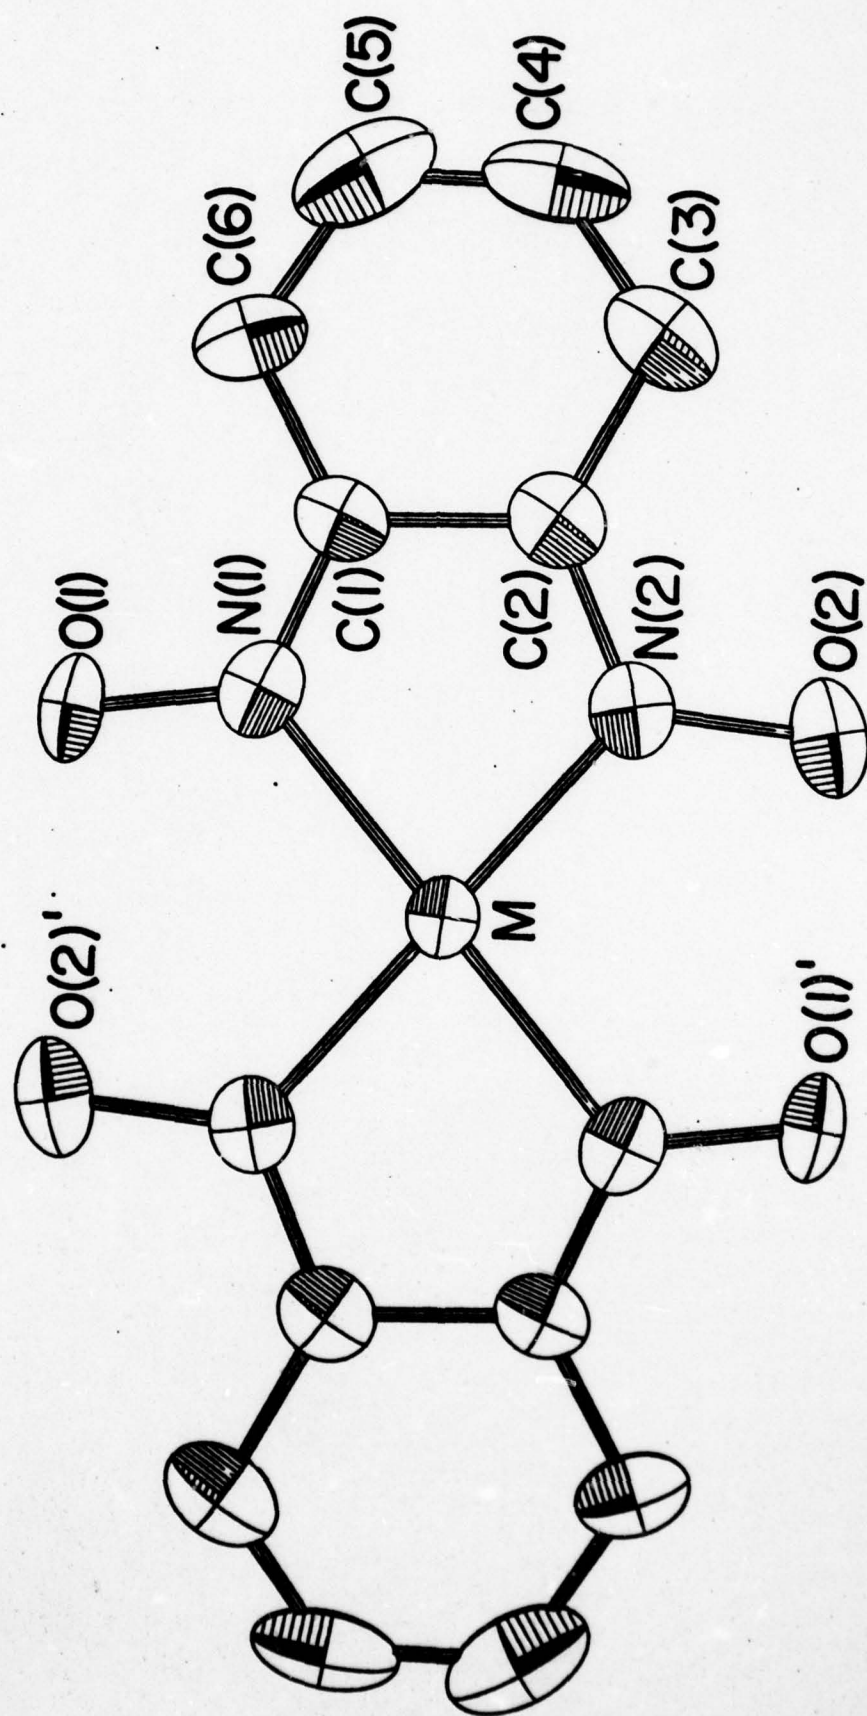


Figure 4. View of the unit cell of $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52 \text{ o-dichlorobenzene}$ along the stacking direction. The \underline{a} - and \underline{b} - axes are in the plane of the page, and the \underline{c} -axis is towards the reader. The vibrational ellipsoids are drawn at the 50% level; the dark circle is an iodine atom.

Tcp.

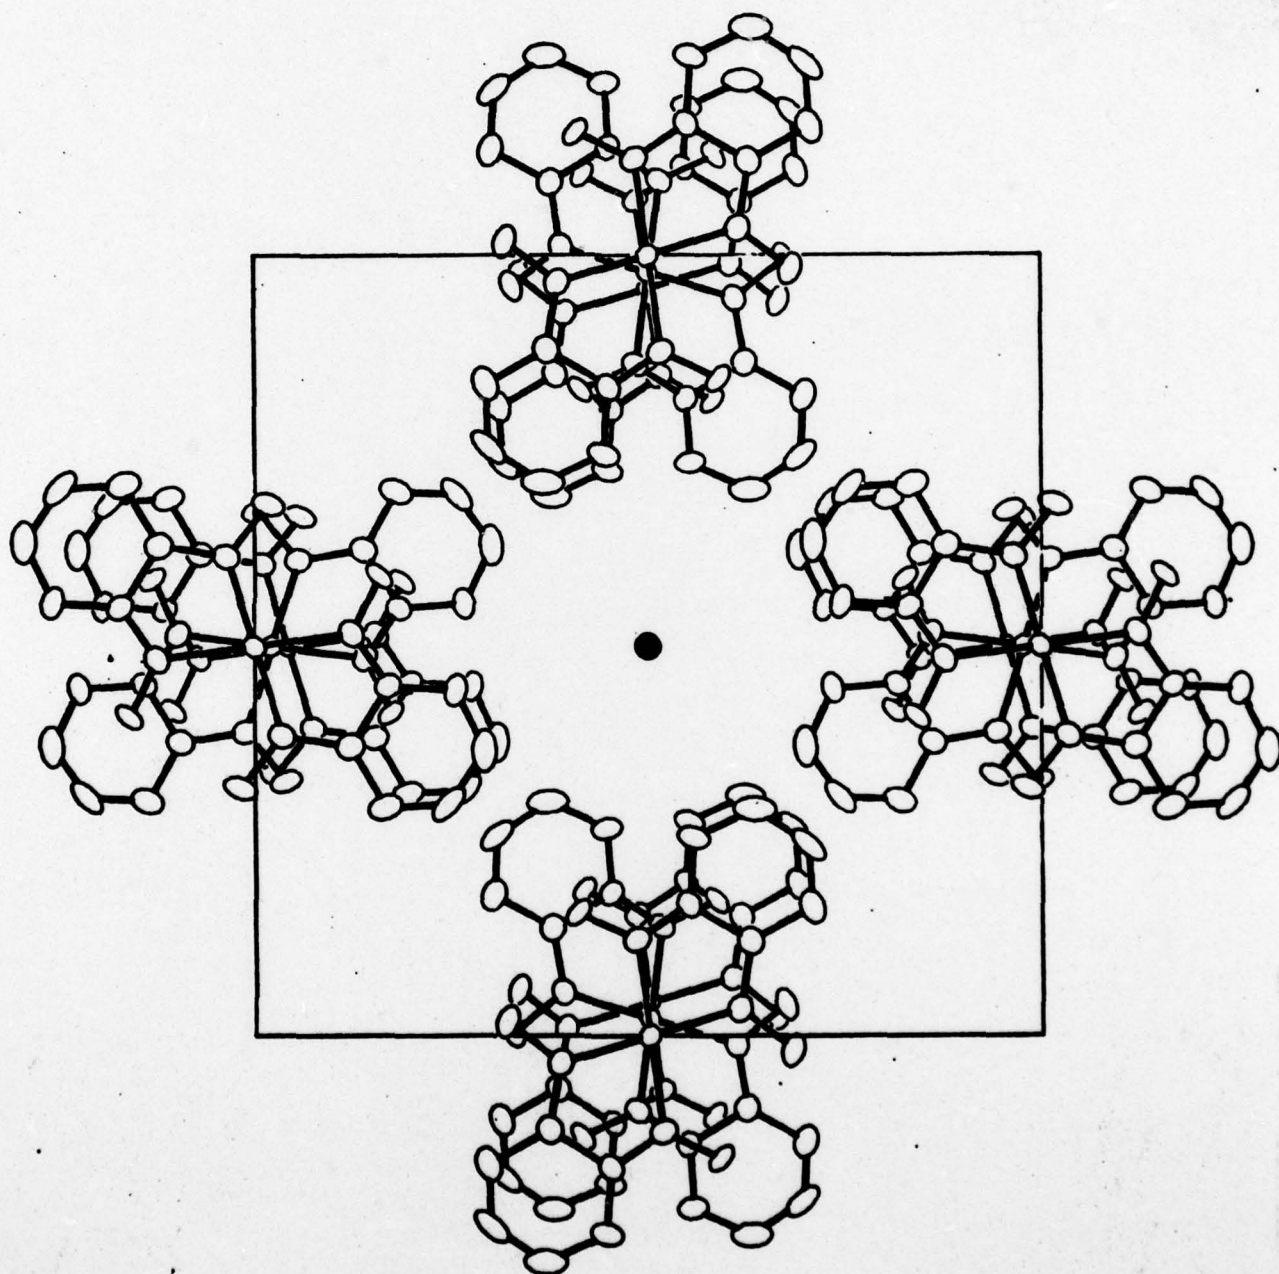


Figure 5. Electronic spectra of polycrystalline (Nujol mulls) samples of
A. $\text{Pd}(\text{bqd})_2\text{I}_{0.80} \cdot 0.52 \text{ o-C}_6\text{H}_4\text{Cl}_2$, B. $\text{Pd}(\text{bqd})_2$, C. $\text{Ni}(\text{bqd})_2\text{I}_{0.52} \cdot 0.32$
toluene, D. $\text{Ni}(\text{bqd})_2$, E. $(\text{benzamide})_2\text{H}^+\text{I}_3^-$.

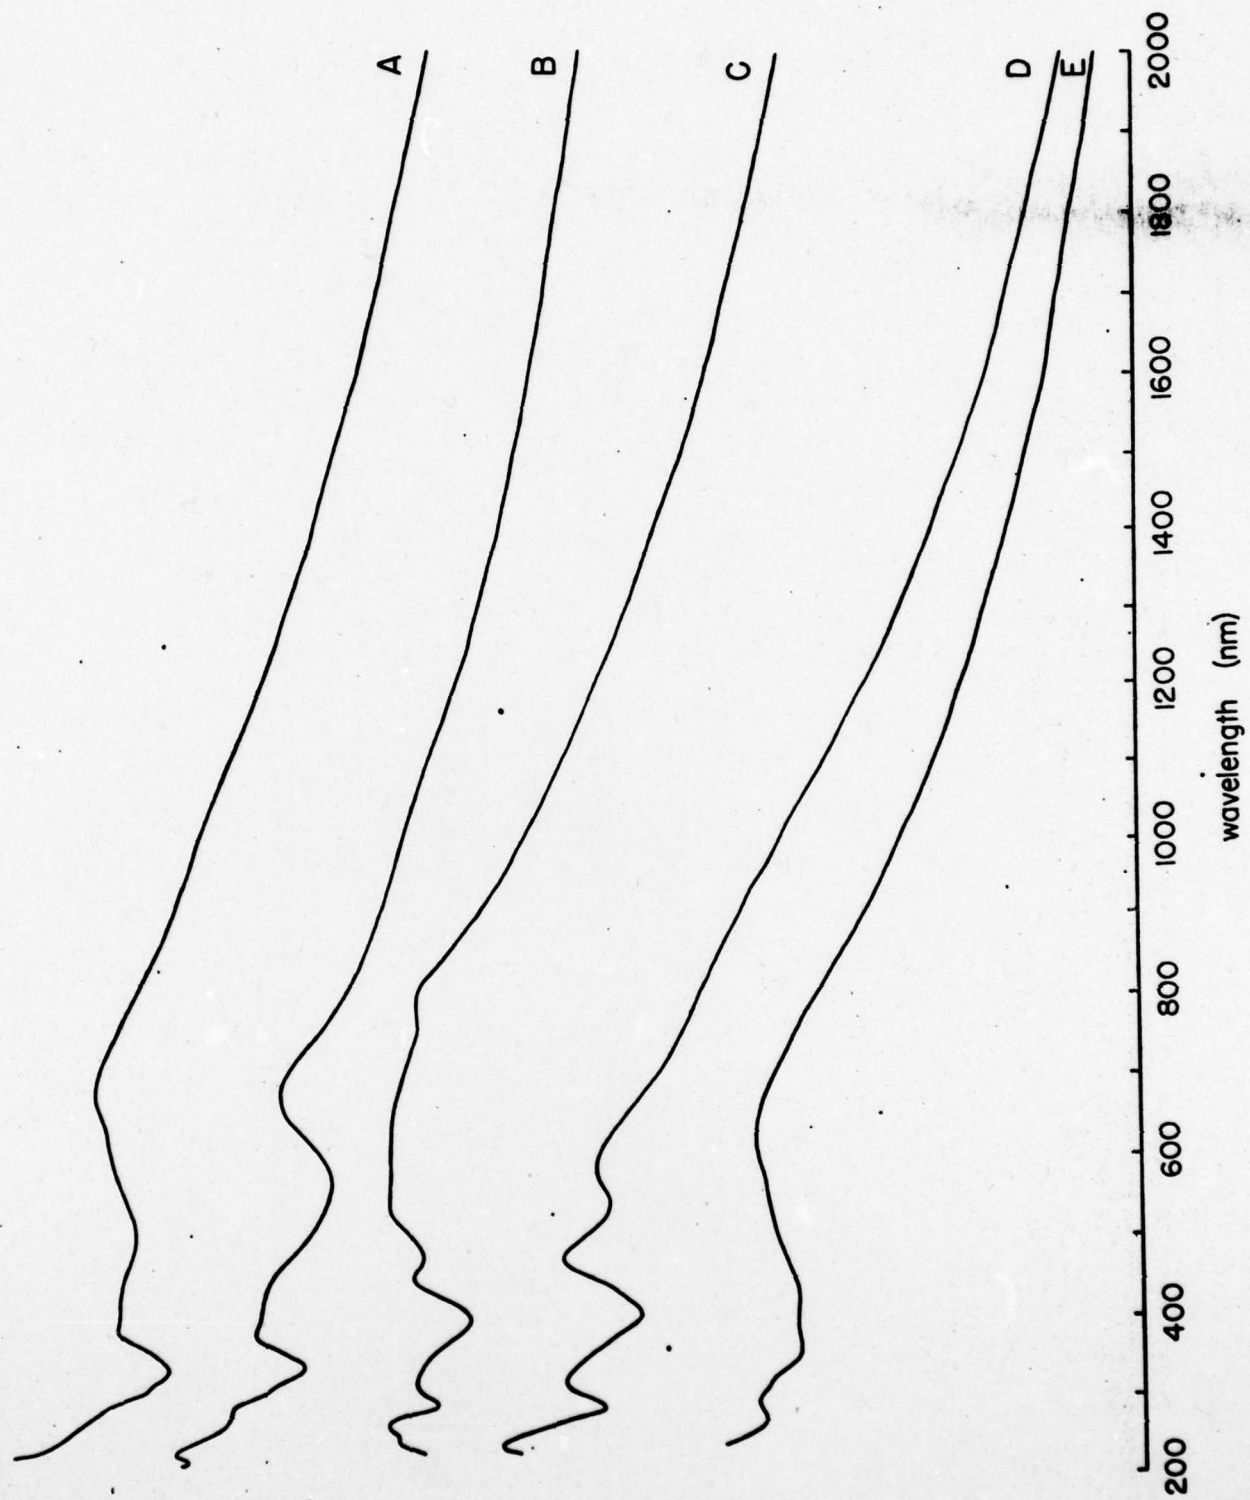


Figure 6. Packing diagram of $\text{Ni}(\text{bqd})_2$ plotted from the data of reference 9.

Vibrational ellipsoids are drawn at the 50% level.

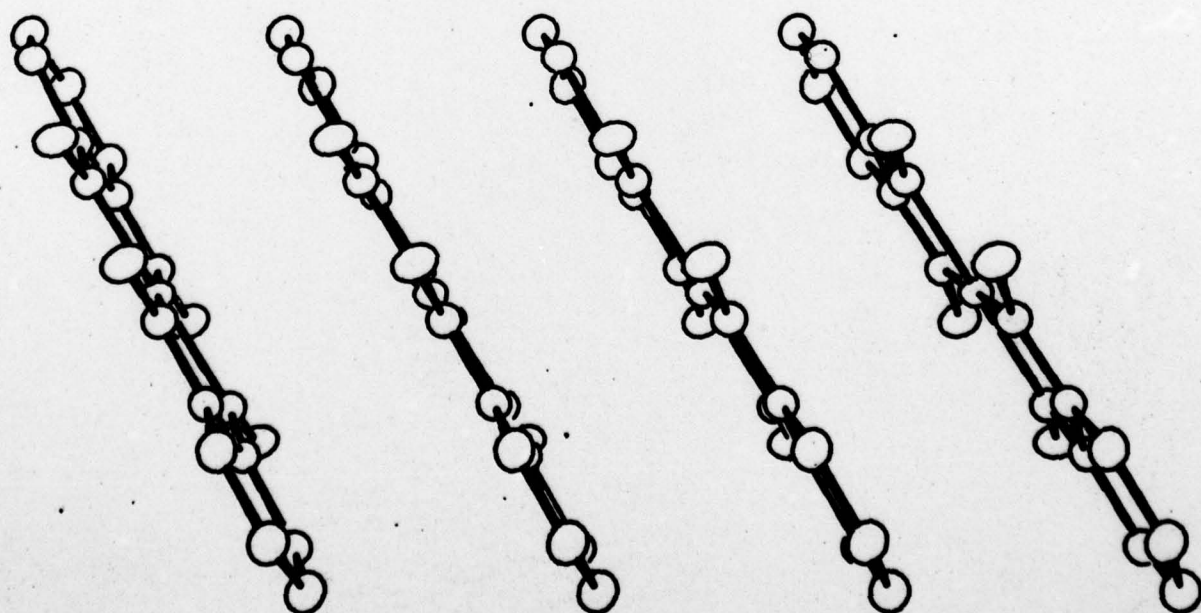
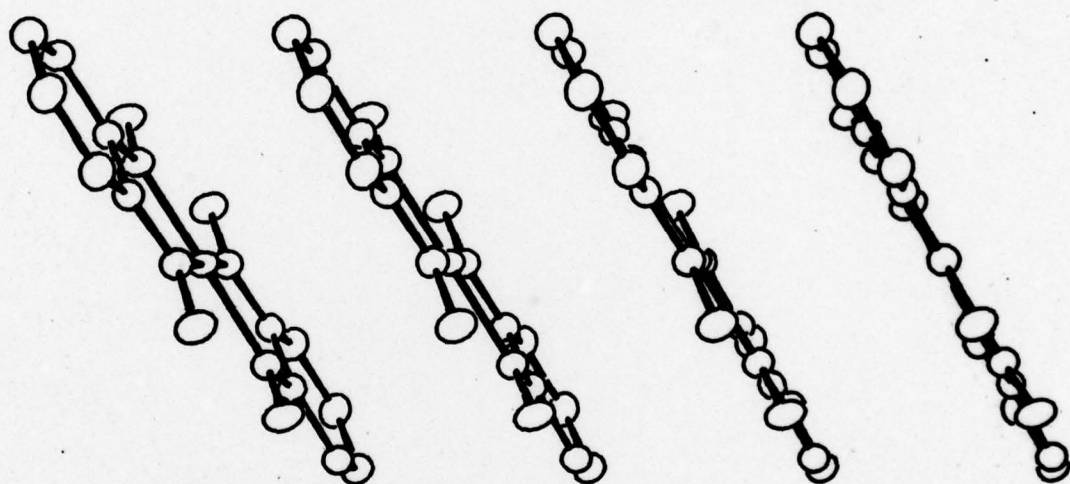
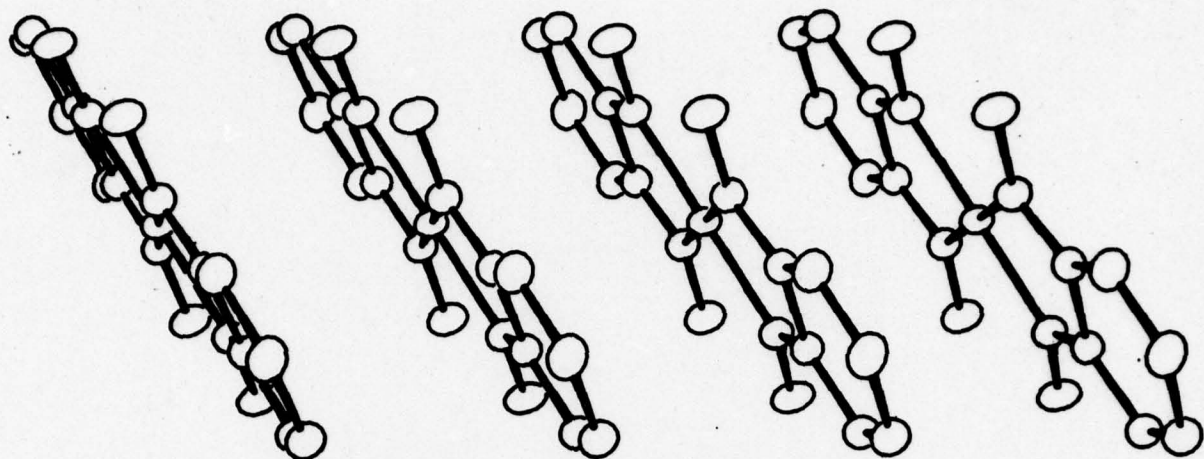


Figure 7. Comparison of metal bisbenzoquinonedioximate crystal structures viewed along the stacking direction.

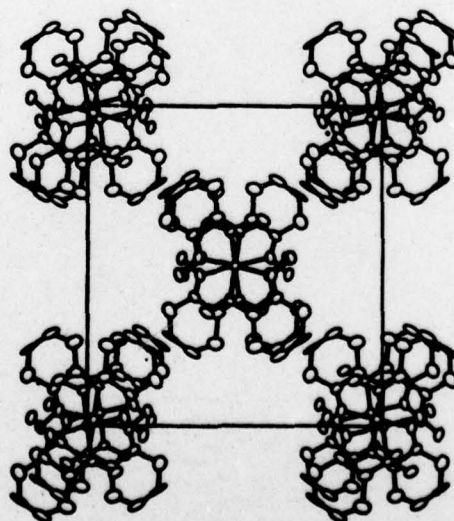

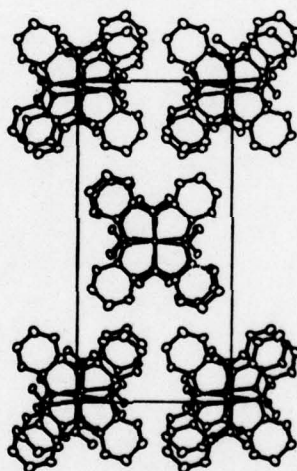

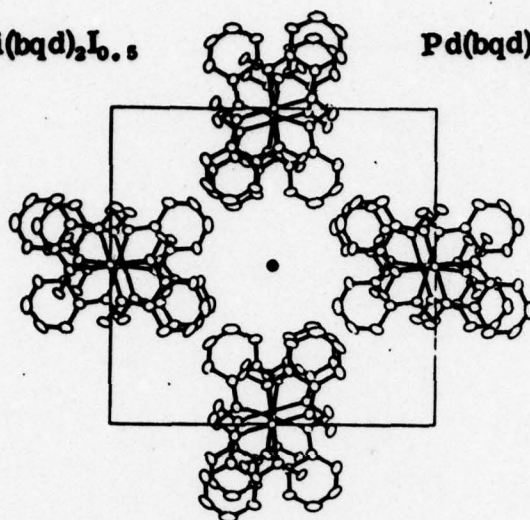




Figure 8. Electrical conductivity (dc) of representative $\text{Ni}(\text{bqd})_2\text{I}_{0.50} \cdot 0.24$ toluene crystals as a function of temperature. Data are measured in the crystallographic c direction.


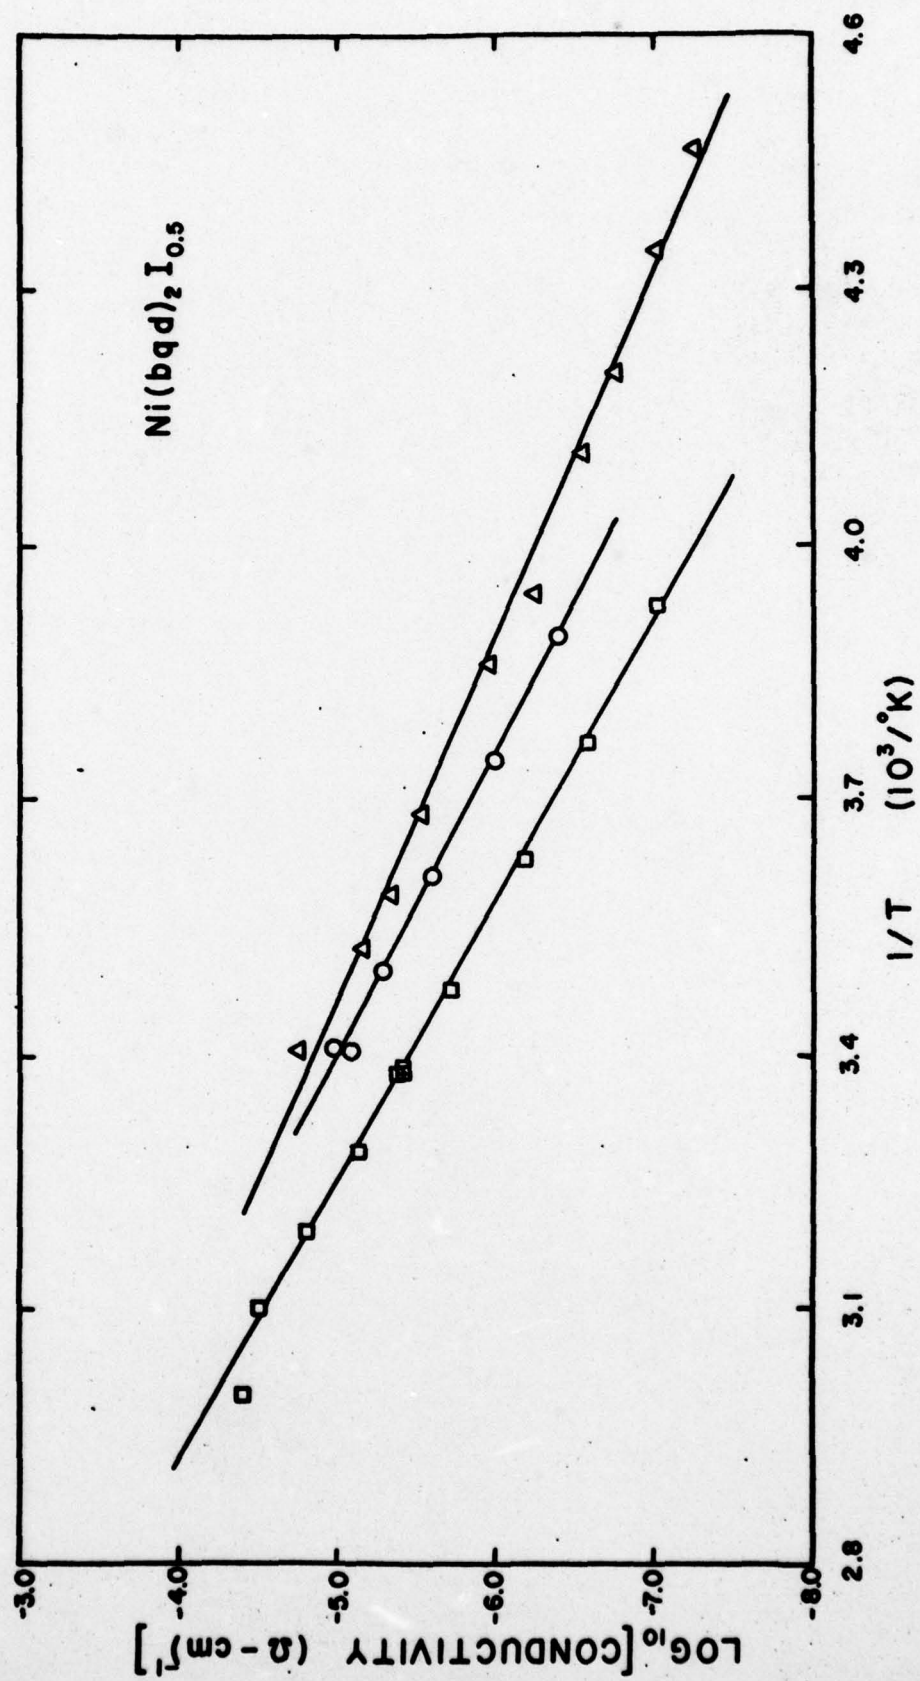


Figure 9. Electrical conductivity (dc) in the crystallographic c direction of representative $\text{Pd}(\text{bqd})_2\text{I}_{0.50} \cdot 0.52$ o -dichlorobenzene crystals as a function of temperature.

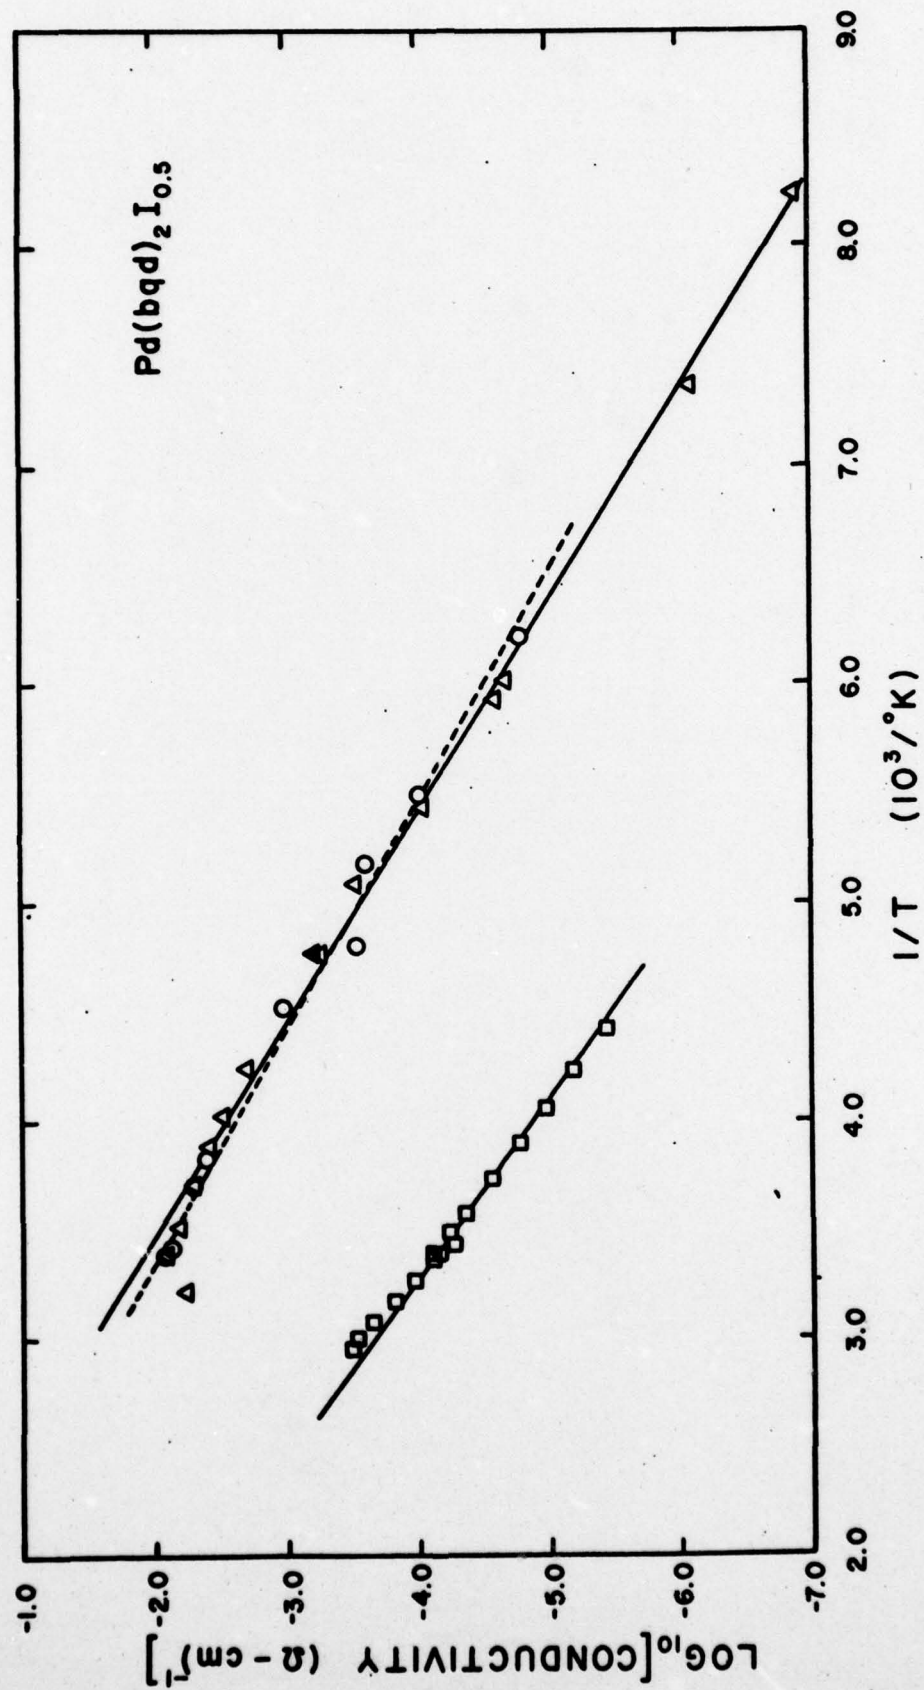

TECHNICAL REPORT DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Arlington, Virginia 22217 Attn: Code 472	2	Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12
Office of Naval Research Arlington, Virginia 22217 Attn: Code 102IP 1	6	U.S. Army Research Office P.O. Box 12211 Research Triangle Park, N.C. 27709 Attn: CRD-AA-IP	1
ONR Branch Office 536 S. Clark Street Chicago, Illinois 60605 Attn: Dr. Jerry Smith	1	Naval Ocean Systems Center San Diego, California 92152 Attn: Mr. Joe McCartney	1
ONR Branch Office 715 Broadway New York, New York 10003 Attn: Scientific Dept.	1	Naval Weapons Center China Lake, California 93555 Attn: Head, Chemistry Division	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106 Attn: Dr. R. J. Marcus	1	Naval Civil Engineering Laboratory Port Hueneme, California 93041 Attn: Mr. W. S. Haynes	1
ONR Branch Office 760 Market Street, Rm. 447 San Francisco, California 94102 Attn: Dr. P. A. Miller	1	Professor O. Heinz Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
ONR Branch Office 495 Summer Street Boston, Massachusetts 02210 Attn: Dr. L. H. Peebles	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
Director, Naval Research Laboratory Washington, D.C. 20390 Attn: Code 6100	1	Office of Naval Research Arlington, Virginia 22217 Attn: Dr. Richard S. Miller	1
The Asst. Secretary of the Navy (R&D) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1		
Commander, Naval Air Systems Command Department of the Navy Washington, D.C. 20360 Attn: Code 310C (H. Rosenwasser)	1		

TECHNICAL REPORT DISTRIBUTION LIST

<u>No. Copies</u>		<u>No. Copies</u>
	Dr. R. M. Grimes University of Virginia Department of Chemistry Charlottesville, Virginia 22901	1
	Dr. M. Tsutsui Texas A&M University Department of Chemistry College Station, Texas 77843	1
	Dr. C. Quicksall Georgetown University Department of Chemistry 37th & O Streets Washington, D.C. 20007	1
	Dr. M. F. Hawthorne University of California Department of Chemistry Los Angeles, California 90024	1
	Dr. D. B. Brown University of Vermont Department of Chemistry Burlington, Vermont 05401	1
	Dr. W. B. Fox Naval Research Laboratory Chemistry Division Code 6130 Washington, D.C. 20375	1
	Dr. J. Adcock University of Tennessee Department of Chemistry Knoxville, Tennessee 37916	1
	Dr. A. Cowley University of Texas Department of Chemistry Austin, Texas 78712	1
	Dr. W. Hatfield University of North Carolina Department of Chemistry Chapel Hill, North Carolina 27514	1
	Dr. D. Seyferth Massachusetts Institute of Technology Department of Chemistry Cambridge, Massachusetts 02139	1
	Dr. M. H. Chisholm Princeton University Department of Chemistry Princeton, New Jersey 08540	1
	Dr. B. Foxman Brandeis University Department of Chemistry Waltham, Massachusetts 02154	1
	Dr. T. Marks Northwestern University Department of Chemistry Evanston, Illinois 60201	1
	Dr. G. Geoffrey Pennsylvania State University Department of Chemistry University Park, Pennsylvania 16802	1
	Dr. J. Zuckerman University of Oklahoma Department of Chemistry Norman, Oklahoma 73019	1