

AD-A059 946

ROCKWELL INTERNATIONAL THOUSAND OAKS CALIF SCIENCE --ETC F/G 11/6
MECHANICAL BEHAVIOR OF TITANIUM ALLOYS (EFFECTS OF HYDROGEN ON --ETC(U)
SEP 78 L A AHLBERG, O BUCK, N F PATON

N00014-76-C-0598

UNCLASSIFIED

SC5056.3TR

NL

| OF |
AD
A059946



END
DATE
FILMED
12-78

DDC

SC5056.3TR

DDC FILE COPY AD A059946

12

SC5056.3TR

COPY NO. 10

LEVEL

MECHANICAL BEHAVIOR OF TITANIUM ALLOYS

TECHNICAL REPORT

Submitted to:
Office of Naval Research



By:

L. A. Ahlberg, O. Buck, and N. E. Paton

Approved for Public Release; Distribution Unlimited.



Rockwell International
Science Center

78 10 06 108



Rockwell International
Science Center

SC5056.3TR

MECHANICAL BEHAVIOR OF TITANIUM ALLOYS
(Effects of Hydrogen on Anisotropic Elastic
Properties of bcc Ti Alloys)

February 1977 to February 1978

Submitted to:
Office of Naval Research
800 N. Quincy St.
Arlington, VA 22217

Attn: Dr. Bruce MacDonald
M/F: Contract No. N00014-76-C-0598

23 September 1978

78 10 06 108

¹
C/1197A/nb

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) MECHANICAL BEHAVIOR OF TITANIUM ALLOYS (Effects of Hydrogen on Anisotropic Elastic Properties of bcc Ti Alloys),	5. TYPE OF REPORT & PERIOD COVERED Technical Report. February 1977-February 1978	6. PERFORMING ORG. REPORT NUMBER SC5056.3TR
7. AUTHOR(s) L. A. Ahlberg, O. Buck, and N. E. Paton	8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0598	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Science Center, Rockwell International 1049 Camino Dos Rios Thousand Oaks, CA 91360	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 471	
11. CONTROLLING OFFICE NAME AND ADDRESS Dr. Bruce MacDonald Office of Naval Research 800 N. Quincy, Arlington, VA 22217	12. REPORT DATE 23 September 1978	13. NUMBER OF PAGES 9
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 12 11p.	15. SECURITY CLASS. (of this report) UNCLASSIFIED	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release; Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Titanium, Hydrogen, Second Order Elastic Constants		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The effects of hydrogen in solid solution on the anisotropic second order elastic constants of Ti-40V and their temperature coefficients have been determined. Using recently published pressure derivatives of hydrogen-free materials we were able to separate out intrinsic alloying effects (due to hydrogen doping) from those due to the accompanying lattice parameter change. The intrinsic effects, which are electronic in nature, are found to be positive and those due to the lattice parameter change are negative. Furthermore, (Continued)		

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

389 949

LB

~~UNCLASSIFIED~~
SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

it is shown that the anisotropy factor increases with increasing hydrogen concentration. Some implications of these observations are briefly discussed.

ACCESSION for	
NTIS	Write Section ☒
DDC	B. H. Section ☐
UNCLASSIFIED	☐
JCS	☐
BY	
DISTRIBUTION/AVAILABILITY CODES	
01	
A	

UNCLASSIFIED
SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)



SC5056.3TR

EFFECTS OF HYDROGEN ON ANISOTROPIC ELASTIC
PROPERTIES OF bcc Ti-ALLOYS

L. A. Ahlberg, O. Buck, and N. E. Paton
Rockwell International Science Center
Thousand Oaks, California 91360 USA

The relatively large effects of hydrogen on yield strength, Young's modulus (and its temperature dependence) and the lattice parameter of metastable (bcc) Ti-alloys have been known for some time (1-4). In this class of materials, the room temperature solubility of H is quite large, so that hydride formation does not interfere with the measurements. Some of the work (2) showed that both yield strength and Young's modulus decrease with increasing H content, while the lattice parameter increases. These results have been interpreted in terms of a predominantly electronic interaction between H and the host lattice. It is now known (5) from the H dependence of second order elastic constants and the lattice parameter, as well as third order elastic constants, that the observed changes in second order constants can be separated into those due to volume changes and those from intrinsic alloying modifications of the interatomic forces, the latter being basically electronic in nature. Since third order elastic constants for the Ti-V system have been determined recently (6), it seemed worthwhile to measure the hydrogen sensitivity of the (anisotropic) second order elastic constants (a combination of which determines the Young's modulus). Such information would allow us to obtain insight into the physical effects of H on the alloy system and its effect on the plastic deformation of bcc metals (7). The present note reports on some of our observations on the Ti-V-H system.



SC5056.3TR

As described earlier (8), an ultrasonic phase comparison technique was used to determine both the values of the pure-mode ultrasonic sound velocities (at about 12 MHz) and their dependence on H and temperature. From these data, the second order elastic constants C_{ij} can be determined (9). The specimen used for these measurements was a single crystal of Ti-40V alloy which was cut to expose a parallel pair of $\{100\}$ faces (0.516 cm apart) and a parallel pair of $\{110\}$ faces (0.848 cm apart). This specimen was charged in a micro-Sieverts apparatus with various amounts of H at 800°C.

Table I summarizes the second order elastic constants C_{11} and C_{44} , as well as important combinations of C_{ij} such as $C' = (C_{11} - C_{12})/2$ (a shear constant) and $B = (C_{11} + 2 C_{12})/3$ (the bulk modulus), as a function of four hydrogen levels. Furthermore, the anisotropy factor $A = C_{44}/C'$, which is a measure of the lattice instability, is given in Table I. This quantity A is of some interest to the present studies since the metastable Ti-V alloys undergo a lattice transformation [the athermal $\beta \rightleftharpoons \omega$ transformation (10)] at low temperatures, which seems to be affected by the presence of H (3). As was pointed out by Zener (11), bcc lattices with a large A tend to be unstable and effects of H on A should give an indication of the transformation behavior of the alloy. As seen from Table I, C' is the elastic property that is most severely affected by H (in the average about -2.6% per a/o H). Therefore, A is rapidly increasing with H, indicating that the lattice becomes more unstable. We also noticed that the attenuation of the acoustic signal, that is used to determine C, increases sharply with increasing H concentration. This attenuation is caused by the $\beta \rightleftharpoons \omega$ transformation, as discussed earlier (1-4). Thus, the large changes in A, C' , and the attenuation suggest



SC5056.3TR

strongly that the $\beta \rightleftharpoons \omega$ transformation temperature is raised with increasing H concentration.

Table II summarizes the temperature dependence of the quantities given in Table I. Particularly noticeable is the change in sign for dC_{11}/dT and dC'/dT (and therefore dA/dT) with increasing H concentration. It is now clear that the change in temperature behavior of the Young's modulus with increasing H, as observed on both Ti-V (3) and Ti-Mo (2.4) alloys at room temperature, is mainly due to either the contribution from dC_{11}/dT or dC'/dT or both.

Based on the present second order elastic constants data and their changes with H concentration, we can now separate the extent to which the observed changes are caused by the intrinsic alloying effect (isovolumetric changes) from those due to the lattice parameter change, which accompanies the addition of hydrogen. This was recently demonstrated for the NbH system (5), where it was postulated that any elastic modulus M is a function of H concentration, c, and the average lattice spacing, a, so that the total change with c can be written as

$$\frac{dM}{dc} = \left. \frac{\partial M}{\partial c} \right|_a + \left. \frac{\partial M}{\partial a} \right|_c \frac{da}{dc} \quad (1)$$

Rewriting Equation (1) yields the relative intrinsic alloying effect

$$\frac{1}{M} \left. \frac{\partial M}{\partial c} \right|_a = \frac{1}{M} \frac{dM}{dc} - \frac{1}{M} \left. \frac{\partial M}{\partial a} \right|_c \frac{da}{dc} \quad (2)$$

with

$$\frac{1}{M} \left. \frac{\partial M}{\partial a} \right|_c \frac{da}{dc} = - \frac{B}{M} \frac{dM}{dp} \frac{3}{a} \frac{da}{dc} \quad (3)$$



SC5056.3TR

where dM/dp is the pressure derivative of a modulus M and a the lattice parameter. dM/dp have been measured recently (6) for 0 a/o H and are given in Table III. da/dc was determined in the present investigation to be $da/dc = 6.9 \times 10^{-4}$ per a/o H. We thus are able to estimate the intrinsic alloying effect for $M = C_{11}$, C_{44} , B , and C' with the results given in Table IV. As one might expect, these intrinsic effects (electronic in nature) of H on the moduli M turn out to be positive and those due to the lattice parameter change are all negative.

These results open up further avenues of research. For instance, the authors believe that an accurate knowledge of the anisotropic elastic moduli will be useful to determine the H dependent shear stress τ , necessary to move a dislocation on the appropriate slip plane (12). On the other hand, the data may give us a better understanding on the effects of H on the $\beta \rightleftharpoons \omega$ transformation. Our results show that the anisotropy factor A increases with increasing H concentration. As indicated in Fig.1, plotting A as a function of V concentration and as a function of H in Ti-40V yields (at low H concentrations) basically the same slope for both curves if the addition of 1 a/o H is equivalent to the extraction of 1 a/o V. Such an equivalence was speculated about earlier (3) without quantitative proof. The meaning of this observation would be that the hydrogen attracts basically one electron from the vanadium. Furthermore, we should note that the effects of H on C' are so large [in particular in respect to NbH (5)] that there is good reason to believe that the H (actually H^- , if the previous statement is valid) gives rise to a large tetragonal distortion of the Ti-V lattice (13).



SC5056.3TR

ACKNOWLEDGEMENT

This work was supported by the Office of Naval Research under Contract No. F00014-76-C-0598.

REFERENCES

1. A. W. Sommer, S. Motokura, K. Ono, and O. Buck, *Acta Met.*, 21, 489 (1973)
2. N. E. Paton, O. Buck, and J. C. Williams, *Scripta Met.*, 9, 687 (1975)
3. O. Buck, D. O. Thompson, N. E. Paton, and J. C. Williams, in Internal Friction and Ultra-sonic Attenuation in Crystalline Solids, Vol. 1, D. Lenz and K. Lucke, Eds., Springer Verlag, Berlin, p. 451 (1975).
4. N. E. Paton and O. Buck, in Effects of Hydrogen on Behavior of Materials (A. W. Thompson and I. M. Bernstein, Eds.), AIME, New York, p. 83 (1976)
5. O. Buck, L. A. Ahlberg, L. J. Graham, G. A. Alers, and C. A. Wert, submitted to *J. Phys. Chem. Sol.*
6. K. W. Katahara, Ph.D. Thesis, Geology and Geophysics Department, University of Hawaii (1977).
7. J. W. Christian in Proceedings II Conf, on the Strength of Metals and Alloys, Am. Soc. for Metals, p. 51 (1970).
8. L. J. Graham, H. Nadler, and R. Chang, *J. Appl. Phys.*, 39, 3025 (1968).
9. H. J. McSkimin, *J. Acoust. Soc. Am.*, 22, 413 (1950).
10. D. deFontaine, N. E. Paton, and J. C. Williams, *Acta Met.*, 19, 1153 (1971).
11. C. Zener, Elasticity and Anelasticity of Metals, University of Chicago Press, Chicago (1948).
12. A. Seeger and G. Schock, *Acta Met.*, 1, 519 (1953).
13. E. S. Fisher, D. A. Westlake, and S. T. Ockers, *Phys. Stat. Sol.* (a) 28, 591 (1975)



SC5056.3TR

TABLE I

Anisotropic second order elastic constants of Ti-40V, doped with H, at 22.5°C.
All values, except A (dimensionless), in 10^{11} dyn/cm².

	0 a/oH	2.4 a/oH	3.6 a/oH	4.8 a/oH
C ₁₁	14.88	14.77	14.65	14.45
C ₄₄	4.053	4.076	4.085	4.104
C	2.399	2.293	2.223	2.114
B	11.880	11.710	11.690	11.630
A	1.690	1.780	1.840	1.940

TABLE II

Temperature derivatives of the second order elastic constants
of Ti-40V doped with H, at 22.5°C. Units of first four
derivatives in 10^7 dyn/cm² °C. dA/dT: in 10^{-4} /°C.

	0 a/oH	2.4 a/oH	3.6 a/oH	4.8 a/oH
dC ₁₁ /dT	-17.84	-10.43	-4.37	+9.33
dC ₄₄ /dT	-4.18	-4.04	-3.77	-2.88
dC'/dT	-6.71	-1.60	+0.44	+7.88
dB/dT	-8.89	-8.30	-4.96	-1.18
dA/dT	+2.99	-0.52	-2.06	-8.60



SC5056.3TR

TABLE III

Pressure derivatives of second order elastic constants of Ti-38.5V,
from Reference 6 (all units dimensionless).

dC_{11}/dP	dC_{44}/dP	dC'/dP	dB/dP
4.63	0.431	0.533	3.92

TABLE IV

The effects of H on the moduli on Ti-40V (all units in 10^{-3} per a/oH)

1st column: measured values.

2nd Column: changes due to lattice expansion.

3rd column: Changes due to intrinsic effects.

M	$\frac{1}{M} \frac{dM}{dc}$	$\frac{1}{M} \frac{\partial M}{\partial a} \left \frac{da}{dc} \right _c$	$\frac{1}{M} \frac{\partial M}{\partial c} \Big _a$
C_{11}	-6.02	-7.65	+1.63
C_{44}	+2.42	-0.26	+2.68
C'	-2.47	-5.46	+2.99
B	-2.73	-8.11	+5.98



SC5056.3TR

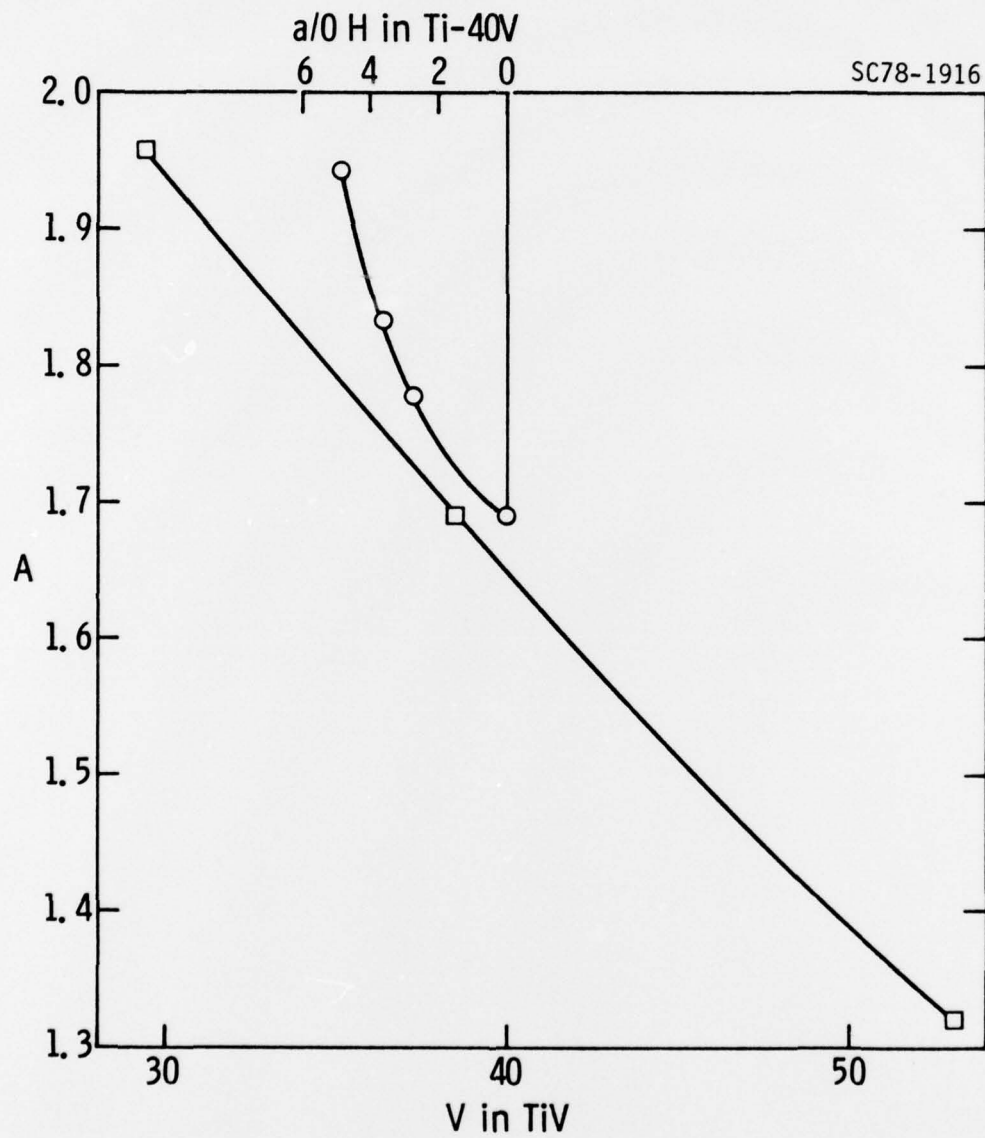


Fig. 1. The change of anisotropy factor with vanadium in Ti-V (6) and hydrogen concentration in Ti-40V.