

AD-A089 916

PENNSYLVANIA STATE UNIV UNIVERSITY PARK DEPT OF CHEMISTRY F/6 7/3
SYNTHESIS OF ALKYLPHOSPHAZENE HIGH POLYMERS VIA THE POLYMERIZAT-ETC(U)
SEP 80 H R ALLCOCK, R J RITCHIE, P J HARRIS N00014-75-C-0685

UNCLASSIFIED

TR-16

NL

1 of 1
9/1/80




END

DATE

FILMED

11-80

DTIC

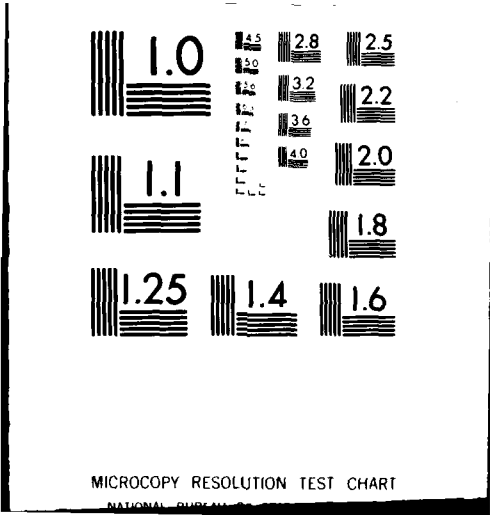

MICROCOPY RESOLUTION TEST CHART

NATIONAL BUREAU OF STANDARDS-1963-A

12

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 16	2. GOVT ACCESSION NO. AD-A089	3. RECIPIENT'S CATALOG NUMBER 976
4. TITLE (and Subtitle) SYNTHESIS OF ALKYLPHOSPHAZENE HIGH POLYMERS VIA THE POLYMERIZATION OF MONOALKYLPENTACHLOROCYCLO- TRIPHOSPHAZENES, $N_3P_3Cl_5R$		5. TYPE OF REPORT & PERIOD COVERED Interim Technical Report
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) Harry R. Allcock*, Robert J. Ritchie, and Paul J. Harris		8. CONTRACT OR GRANT NUMBER(s) N00014-75-C-0685
9. PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry, The Pennsylvania State University, University Park, Pa. 16802		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 356-577
11. CONTROLLING OFFICE NAME AND ADDRESS Department of the Navy, Office of Naval Research, Arlington, Va. 22217		12. REPORT DATE September 22, 1980
		13. NUMBER OF PAGES 32
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) LEVEL IV		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this report) Distribution unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Accepted for publication in Macromolecules		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Polymers, phosphazenes, alkylphosphazenes, polymerization		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) A new class of high molecular weight poly(organophosphazenes) has been prepared by the thermal polymerization of monoalkylcyclotriphosphazenes, $N_3P_3Cl_5R$. These are among the first high molecular weight polyphosphazenes with alkyl groups linked directly to the skeleton through C-P bonds. Elastomers were obtained by the replacement of the chlorine atoms in the polymers by trifluoroethoxy or phenoxy groups.		

AD A 089916

SDITIC
SELECTED
OCT 3 1980

DDC FILE COPY

80 9 29 056

Office of Naval Research

Contract No. ¹³ N00014-75-C-0685

Task No. 356-577

⁹ Technical Report No. 16

¹¹ 23 Sep 80

⁶ SYNTHESIS OF ALKYLPHOSPHAZENE HIGH POLYMERS VIA THE POLYMERIZATION

OF ~~MONOPENTACHLOROCYCLOTRIPHOSPHAZENES~~ ^{N₃P₃Cl₅R}
of *nonalkylpentachlorocyclo triphosphazenes*

by

¹³ 29

¹⁰ Harry R. Allcock, Robert J. Ritchie, Paul J. Harris

Accepted for publication in the Journal
Macromolecules

¹⁴ TR-16

Department of Chemistry
The Pennsylvania State University
University Park, Pennsylvania 16802

September 22, 1980

Reproduction in whole or in part is permitted for any
purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

400343 slt

Synthesis of Alkylphosphazene High Polymers via the Polymerization of Monoalkylpentachlorocyclotriphosphazenes, $N_3P_3Cl_5R$ ^{1,2}

Harry R. Allcock*, Robert J. Ritchie, and Paul J. Harris


Contribution from the Department of Chemistry, The Pennsylvania State University, University Park, Pennsylvania 16802

Received

Abstract: A new class of high molecular weight poly(organophosphazenes) of general formula $\{N=P(Cl)_2\}_2-N=P(Cl)R\}_n$ (VIII), where $R = CH_3, C_2H_5, n-C_3H_7,$ or $n-C_4H_9$, have been prepared by the thermal polymerization of monoalkylcyclotriphosphazenes, $N_3P_3Cl_5R$ (VII). These are among the first high molecular weight polyphosphazenes with side groups linked directly to the skeleton through C-P bonds. Hydrolytically stable, elastomeric derivatives of formula, $\{N=P(OR')_2\}_2-N=P(OR')R\}_n$, were obtained by a replacement of the chlorine atoms in VIII with trifluoroethoxy- or phenoxy-groups. Bulky alkyl groups, such as $i-C_3H_7$ or $t-C_4H_9$ retard the polymerization process and sensitize the system to decomposition reactions during polymerization. The structures of the polymers were deduced by comparisons with cyclic trimeric phosphazene model compounds of formula $N_3P_3(OCH_2CF_3)_5R$ and $N_3P_3(OC_6H_5)_5R$, where R is $CH_3, C_2H_5, n-C_3H_7, n-C_4H_9, i-C_3H_7,$ or $t-C_4H_9$.

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A	

A broad range of high molecular weight poly(organophosphazenes) can be prepared by the thermal polymerization of hexachlorocyclotriphosphazene (I) to poly(dichlorophosphazene) (II), followed by nucleophilic replacement of the chlorine atoms in II by alkoxy, aryloxy, or amino substituents.³⁻⁷ The resultant organophosphazene-derivatives (III, IV, or V) are of fundamental and technological interest.⁸⁻¹⁰

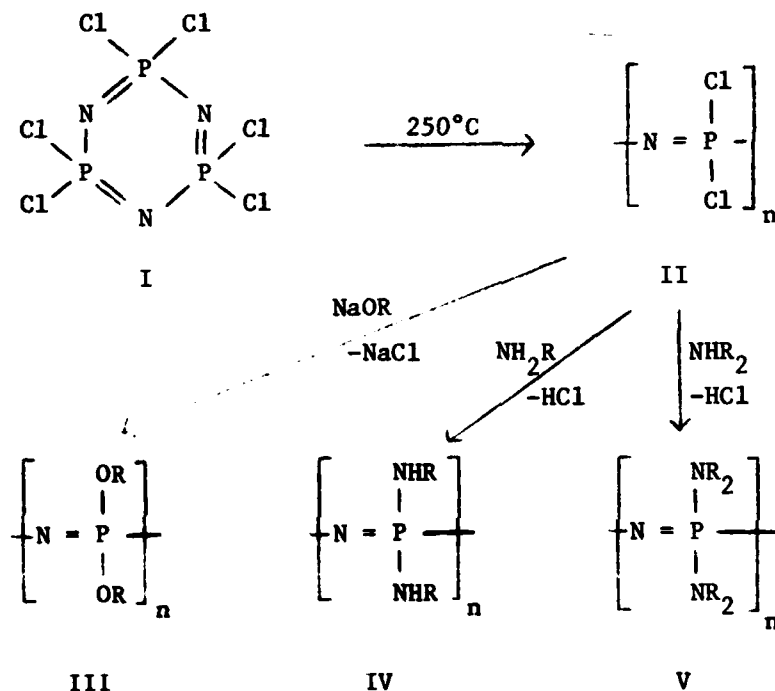

$n \approx 15,000$

Nevertheless, mechanistic and theoretical arguments can be used to show that polyphosphazenes with organic side groups linked directly to phosphorus through C-P bonds should be especially interesting. Specifically, P-C bonded side groups are expected to be less susceptible to high temperature thermal rearrangements than P-O or P-N bonded side groups, and the presence of, say, methyl groups bonded directly to the phosphazene skeleton should change the intramolecular interactions and generate unexpected physical properties.

Two synthetic routes have been explored for the synthesis of poly(alkyl- or aryl-phosphazenes). In the first, poly(dihalophosphazenes), such as II, have been allowed to react with organometallic reagents.¹¹⁻¹³ These reactions

often lead to cleavage of the polymer skeleton.¹² Only when poly(difluoro-phosphazene) is used as a reaction substrate can high degrees of arylation be achieved without extensive chain cleavage.¹³ In the second approach, cyclic oligomeric alkyl- or aryl-phosphazenes have been studied as potential polymerization "monomers."^{14,15} Cyclic phosphazenes such as $(NPPh_2)_3$ or 4 or $(NPM_2)_3$ or 4 have so far resisted thermal polymerization.^{14,15} Even species such as $(NPClPh)_3$ enter into polymerization processes only in copolymerization reactions with $(NPCl_2)_3$ (I).¹⁴


In this present work we have investigated the prospect that monoalkyl-pentachlorocyclo-triphosphazene compounds $N_3P_3Cl_5R$, VII, with only one alkyl group attached to the cyclic trimeric phosphazene ring, might undergo a ring-opening polymerization to yield high molecular weight polymers with alkyl groups bonded directly to the skeletal phosphorus atoms. This would constitute the simplest and most direct route for the synthesis of alkyl-substituted polyphosphazenes. Moreover, it would allow certain theories to be tested even though the fully alkylated polymers of formula $(NPR_2)_n$ were not available.

The main objectives of the work were to answer the following questions:

(1) Is the homopolymerization of chlorocyclophosphazenes inhibited when only one chlorine substituent is replaced by an alkyl group? (2) What effects on the polymerization, if any, would result when a small alkyl group, such as methyl, in VII, is replaced by progressively bulkier alkyl groups? (3) In a chlorocyclophosphazene polymerization process, do the monomer residues enter the polymer in the same linkage sequence as the one that exists in the cyclic trimer? Can the presence of one alkyl group attached to the ring be utilized as a probe to monitor this aspect of the polymerization process? (4) What influence might the alkyl groups have on the physical properties of the high polymers?


Results and Discussion

Synthesis of Monoalkyl-pentachlorocyclotriphosphazenes (VII). The cyclic trimers of general structure VII were synthesized by a new technique reported earlier.¹⁶⁻¹⁸ The method involves the interaction of hexachlorocyclotriphosphazene (I) with alkyl Grignard reagents in the presence of $[\underline{n}\text{-Bu}_3\text{PCuI}]_4$,¹⁹ followed by treatment of the reaction intermediate¹⁶ with i-propanol, to yield hydrido-phosphazenes (VI).^{16,17} Subsequent treatment of VI with chlorine in tetrachloromethane solution led to the formation, in high yield, of the monoalkyl-pentachlorocyclotriphosphazenes (VII).^{17,18} For this study, compounds were prepared in which the R group was CH_3 , C_2H_5 , $\underline{n}\text{-C}_3\text{H}_7$, $\underline{n}\text{-C}_4\text{H}_9$, $\underline{i}\text{-C}_3\text{H}_7$, or $\underline{t}\text{-C}_4\text{H}_9$. The characterization data for these compounds have been discussed in another paper.¹⁸

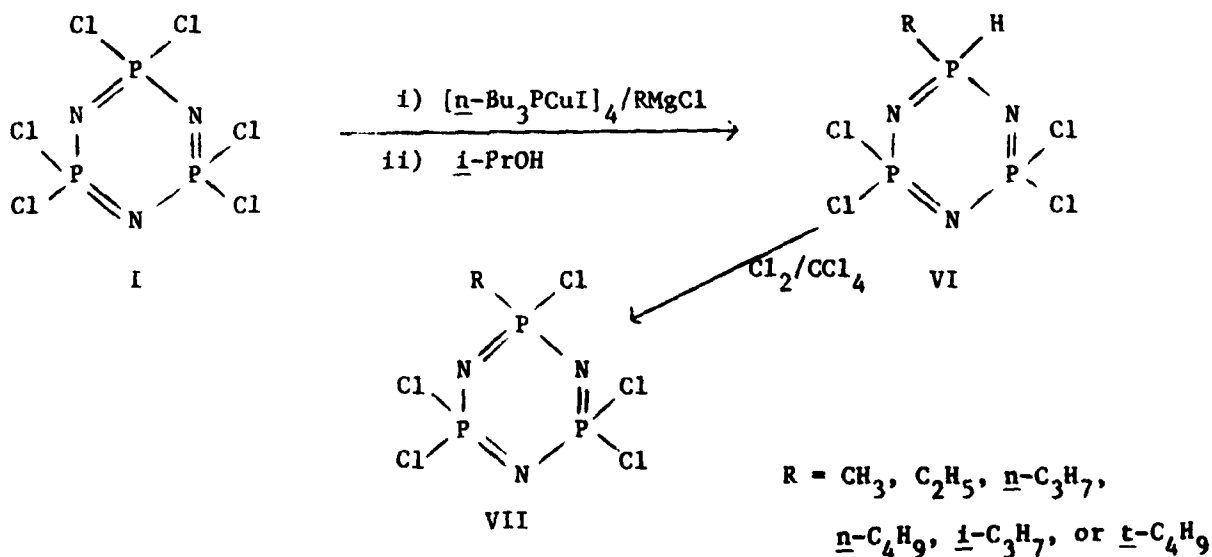

Rigorous steps were taken to ensure the purity of the monoalkyl-penta-chlorocyclotriphosphazene compounds (VII) before polymerization was attempted. The purification procedure involved successive recrystallizations from *n*-hexane, followed by vacuum sublimation or distillation. This procedure was repeated until only one sharp peak was observed when the compound was subjected to vapor phase chromatography/mass spectrometric analysis.²³





Polymerization of VII. Four of the rigorously purified monoalkyl-penta-chlorocyclotriphosphazenes (VII) underwent a thermal polymerization at 250°C to yield high polymers of the general formula VIII.

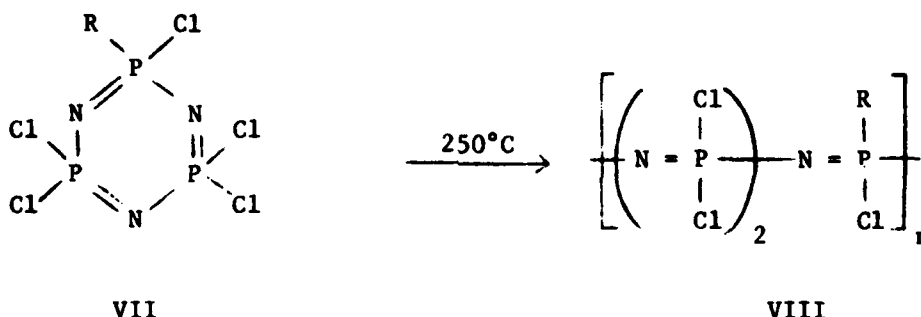

However, marked differences in the polymerization behavior were observed depending on the size of the alkyl group in VII. Those cyclic trimers which contained small alkyl groups, such as methyl or ethyl, were found to polymerize readily within 15-24 h at 250°C. When R was *n*-C₃H₇ or *n*-C₄H₉, longer polymerization times were required (18-36 h), but polymers of type VIII were still formed. However, those species in which R was *i*-C₃H₇ or *t*-C₄H₉ polymerized at a slower rate and yielded discolored crosslinked products. Hydrogen chloride was also liberated during these latter reactions. The mechanisms of these reactions will be discussed in a later section.


Replacement of Chlorine in VIII. (a) Model Compound Studies. Phosphazene polymers that contain P-Cl bonds are hydrolytically unstable.³⁻⁷ Thus, full characterization of the polymers VIII could be undertaken only after the halogen atoms had been replaced by organic residues. However, the reactions of phosphazene high polymers are nearly always more complex than those of the analogous small molecule phosphazenes. Here, in this work (as well as in many of our previous studies),²¹ it was necessary to examine the halogen substitution behavior of cyclic species such as VII as a prelude to performing substitution reactions with the analogous high polymers, VIII. In this way, it was hoped to optimize the substitution reaction conditions and verify that the alkyl groups would not inhibit complete replacement of the halogen atoms or sensitize the system to skeletal cleavage reactions.

All compounds of type VII were found to react cleanly with sodium trifluoroethoxide^{22,23} or sodium phenoxide²⁴ to form the products of formula IX in high yield. Species IX were characterized by the use of a combination of infrared^{25,26} and ^1H and ^{31}P NMR spectroscopy, mass spectrometry (both low and high resolution) and, in representative cases, elemental analysis. These data are listed in Tables I and II.

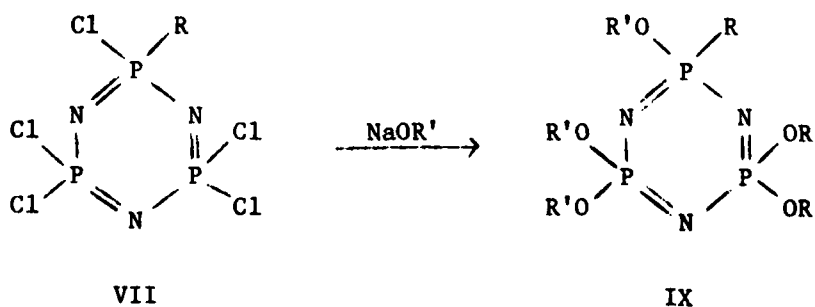


The total replacement of halogen in compounds VII occurred smoothly with all variations of the alkyl group, R. The reactions of VII with sodium trifluoroethoxide were found to proceed readily in boiling tetrahydrofuran. However, the reactions with sodium phenoxide required the use of boiling 1,4-dioxane as a solvent to achieve complete substitution.

Replacement of Chlorine in VIII. Macromolecular Systems. After the optimum conditions for halogen replacement with trifluoroethoxy- or phenoxy-groups had been determined for the cyclic model compounds, VII, these conditions were then employed for halogen replacement reactions with the polymers of type VIII. All four polymers of type VIII, where R was CH₃, C₂H₅, n-C₃H₇ or n-C₄H₉, reacted with sodium trifluoroethoxide with complete replacement of the chlorine atoms to yield the hydrolytically stable derivatives of formula X, (R' = CH₂CF₃). Polymer VIII (R = CH₃) was also allowed to react with sodium phenoxide to yield X (R' = C₆H₅).

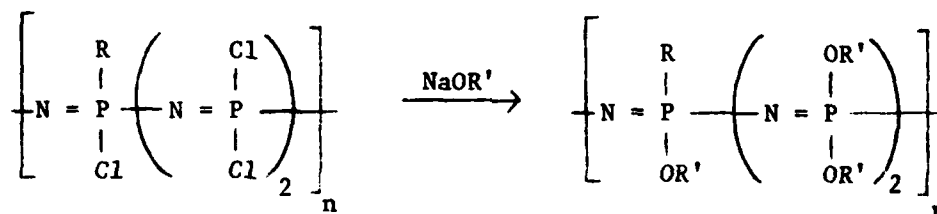

VIII

X



Particular interest was associated with those polymers of type X that contained trifluoroethoxy units as the cosubstituent groups, because a considerable amount of structural and chemical information is available for the related homopolymer of formula, $[\text{NP}(\text{OCH}_2\text{CF}_3)_2]_n$.^{4,6,9}

Characterization and Properties of the Polymers. All the polymers of types VIII and X were characterized by means of infrared and ^1H and ^{31}P NMR spectroscopy. In addition, glass transition temperatures (T_g), GPC molecular weights, and elemental analyses were obtained for polymers of type X. The results are summarized in Tables III and IV.

The infrared spectra^{24,26} of the polymers were compatible with structures VIII or X, with an intense absorbance detected between 1100 and 1300 cm^{-1} . This is characteristic of the $-\text{P}=\text{N}-$ skeleton.⁶ The spectra of polymers of type VIII also showed evidence for the presence of the alkyl groups. The ^1H and ^{31}P NMR data for polymers VIII and X are listed in Table IV. The ^1H NMR spectra of VIII were compatible with the presence of the alkyl groups: a broad resonance was detected, centered between 1.0 and 1.5 δ . The ^1H NMR spectra of polymers X showed two areas of resonance. The resonance from the alkyl group appeared between 1.0 and 1.5 δ . The resonance position for the trifluoroethoxy cosubstituent appeared as a broad multiplet centered at 4.2 δ , while the phenoxy substituent showed a resonance position of 7.1 δ . An integration of the areas under these two sets of peaks suggested a ratio of 1 alkyl group per 5 trifluoroethoxy- or phenoxy-constituents.

The ^{31}P NMR spectra of polymers VIII and X showed two general areas of resonance with considerable fine structure in each region. Representative spectra are shown in the Figure. An integration of the areas under the two envelopes indicated a ratio of 1:2 for the two types of phosphorus atoms present. This was again compatible with the conclusion that an average of one alkyl group per three phosphorus atoms was retained in polymers VIII and X. The fine structure found within the two ^{31}P NMR envelopes was consistent with a variety of microenvironments for the phosphorus atoms in the skeleton, perhaps


complicated by P-P spin-spin or through space coupling. In any case, it seems clear that the spectra are too complicated to be explained by a regular sequencing of repeating sets of the type depicted in VIII or X. Thus, it would appear that the polymerization mechanism of VII does not involve a simple ring cleavage at one specific site followed by an ordered coupling of the linear trimeric fragments. This aspect is discussed in more detail in a later section.

The low temperature properties of polymers of type X were not affected significantly by the presence or the type of the alkyl group, R, bound to the polymer. The glass transition temperatures (listed in Table III) of polymers X were found to be 10-15°C higher than those of the related homo-polymers, $[\text{NP}(\text{OCH}_2\text{CF}_3)_2]_n$ ($T_g = -66^\circ\text{C}$) or $[\text{NP}(\text{OC}_6\text{H}_5)_2]_n$ ($T_g = -8^\circ\text{C}$). However, the room temperature physical properties of the polymers X were very different from those of the non-alkylated analogues. Poly[bis(trifluoroethoxy)phosphazene] is a microcrystalline, film-forming polymer.^{6,8,9} The trifluoroethoxy derivatives of polymers X were elastomers, although the elasticity decreased as the size of the alkyl group increased. The methyl derivative could be stretched readily to 400% of its original length without rupture, while the n-butyl polymer was less extensible (~50% extension before rupture). The phenoxy derivative of polymer X ($R = \text{CH}_3$, $R' = \text{C}_6\text{H}_5$) also displayed elastomeric properties and could be reversibly extended by ~200% without breakage.

The appearance of elastomeric properties following the introduction of the alkyl group R in polymers X was attributed to the role played by the alkyl units in disrupting the molecular symmetry, and thereby reducing microcrystalline order.

The Polymerization Mechanism. The mechanism of polymerization of $(\text{NPCl}_2)_3$ (I) is still only poorly understood even though this reaction has been studied in some detail.⁶ Nevertheless, convincing evidence exists that phosphorus-halogen bonds are a prerequisite for polymerization. It has been suggested that the ionization of a chloride ion from phosphorus (perhaps catalyzed by trace impurities) is an essential requirement for the initiation process.²⁸⁻³¹ It seems reasonable to assume that the mechanism of polymerization of VI is similar to that of I.

Thus, transient intermediates or transition states of the type depicted in XI or XII may participate in the initiation process, with subsequent steps

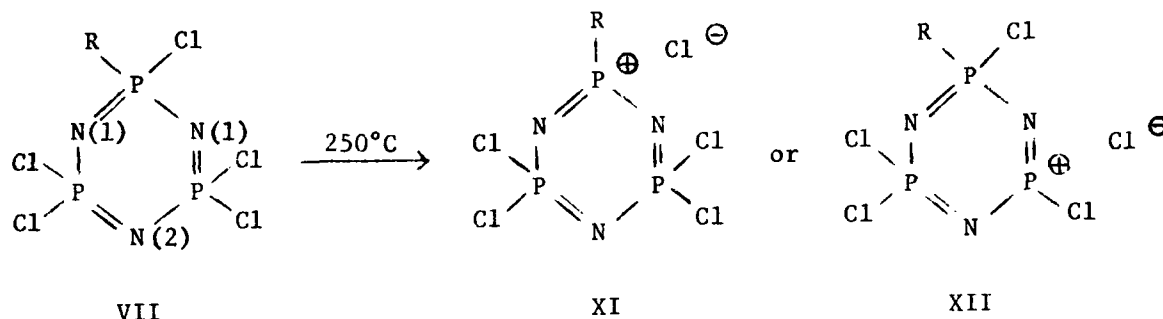

involving a ring-opening attack by the phosphazanium cations XI or XII on the N(1) or N(2) skeletal atoms of VII. If this is true, a high probability exists that a statistically random arrangement of $\text{PCl}(\text{R})$ and PCl_2 groups will be found in the final polymer, even though the ratio of these species remains at 1:2. This interpretation is compatible with the complex patterns observed in the ^{31}P NMR spectra of these polymers (see the Figure). Any alternative interpretation would require a 100% preference for the formation of, say, species XI over XII and a 100% preference for attack at, say, N(1) over N(2). This is highly unlikely. Moreover, because the 1:2 ratio of repeating units was retained in the polymer, it appears that the polymerization mechanism does not involve a prior breakdown of the trimer to a monomer. Monomer units of the type $\text{N}\equiv\text{PCl}(\text{R})$ would be

expected to have a different reactivity in addition reactions from those of the type, $N\equiv PCl_2$.

However, the alkyl group does appear to influence the polymerization process. The molecular weights of the polymers X showed a small but definite decrease as the size of the alkyl group, R, was increased (Table III). Also the time required for polymerization increased with increasing steric bulk of the alkyl group. These results may be ascribed to steric effects involving attack by species such as XI on another trimer ring. Alternatively, they may reflect the influence of side reactions. The detection of hydrogen chloride as a product from the polymerization of $N_3P_3Cl_5(i-C_3H_7)$ or $N_5P_3Cl_5(t-C_4H_9)$, together with concurrent crosslinking, is an indication that alkyl groups (and especially branched alkyl groups) cannot survive intact for extended periods of time in the relatively hostile environment needed to effect polymerization.

Experimental

Materials. Hexachlorocyclotriphosphazene, $(NPCl_2)_3$, obtained from El Monte Chemical Corp., Pasadena, Calif., was purified by fractional sublimation followed by recrystallization from n-hexane, to a final mp of 111.5-112.5°C. The Grignard reagents were commercial products obtained from Aldrich or Alfa Ventron. The copper complex, $[n-Bu_3PCuI]_4$, was prepared as reported in the literature.¹⁹ Tetrahydrofuran (THF) (obtained from Fisher Corp.) was distilled into the reaction flask under an atmosphere of dry nitrogen from a sodium-benzophenone ketyl drying agent. The 1,4-dioxane (obtained from Fisher Corp.) was distilled in a similar manner from sodium metal. Trifluoroethanol (obtained from Halocarbon Products), was dried over molecular sieves (4 Å) before use. The phenol (obtained from Fisher Corp.) was used as received.

Synthesis of $N_3P_3Cl_5R$. All compounds of structure VII ($R = CH_3, C_2H_5, n-C_3H_7, n-C_4H_9, i-C_3H_7, t-C_4H_9$) were prepared as described earlier.¹⁶⁻¹⁸ These compounds were purified for polymerization by either recrystallization and sublimation or by distillation. The compounds were considered "pure" when the vapor phase chromatography/mass spectrometric trace showed only one sharp peak.

Polymerization Techniques. All attempts to polymerize compounds VII were carried out in an identical manner; the following procedure is typical. Monomethyl-pentachlorocyclotriphosphazene, $N_3P_3Cl_5CH_3$, (5.0 g, 0.015 mol), purified as described above, was placed in a Pyrex glass tube (13 mm O.D. x 200 mm) that was constricted ≈ 50 mm from the open end of the tube. The tube was attached to a vacuum line and was evacuated for 30 min., after which time the pressure in the system was 0.05 torr. The tube was then sealed at the constriction, was wrapped in aluminum gauze, and was placed on a rocking device in a Freas thermoregulated oven, pre-heated to a temperature of 250°C. The viscosity of the molten reaction mixture increased during the next 15-36 h. The tube was removed from the oven and was allowed to cool to room temperature. The tube was then opened in a nitrogen filled glove bag and the contents were transferred to a small sublimator. The unpolymerized cyclic trimer was then sublimed from the polymer at 70°C/0.05 torr. Typical conversions to polymer ranged from 50-75%.

When this technique was applied to $N_3P_3Cl_5R$ ($R = i-C_3H_7, t-C_4H_9$), the contents of the tube discolored before any obvious increase in viscosity was noted. Prolonged heating of these compounds (48 h) resulted in the formation of a brown, insoluble material. Hydrogen chloride was detected when the tubes were opened.

Model Compound Halogen Replacement Studies. (a) Reactions with $\text{NaOCH}_2\text{CF}_3$.

The reactions of all cyclic compounds $\text{N}_3\text{P}_3\text{Cl}_5\text{R}$ (VII) with $\text{NaOCH}_2\text{CF}_3$ were carried out in an identical manner. The following is a typical procedure: A solution of sodium trifluoroethoxide in THF (125 mL) was prepared from sodium (3.5 g, 0.15 mol) and trifluoroethanol (20.0 g, 0.20 mol) under an atmosphere of dry nitrogen. A solution of $\text{N}_3\text{P}_3\text{Cl}_5\text{CH}_3$ (5.0 g, 0.015 mol), dissolved in THF (50 mL) was added slowly to the solution of sodium trifluoroethoxide. When the addition was complete, the reaction mixture was heated to reflux for 48 h. After this time, the reaction mixture was allowed to cool to room temperature, was poured into water (250 mL), and was extracted with diethyl ether (2 x 250 mL). The ether layer was dried over magnesium sulfate, and the ether was removed under reduced pressure to leave the crude products as an oil. The product was purified by filtration of a solution in CH_2Cl_2 through neutral alumina and finally by recrystallization from *n*-hexane. Characterization data for the products are listed in Tables I and II. (b) Reactions with NaOC_6H_5 . A similar technique was employed for the reactions of cyclic compounds $\text{N}_3\text{P}_3\text{Cl}_5\text{R}$ (VII) with NaOC_6H_5 . However, it was found that complete substitution was effected more readily in 1,4-dioxane at reflux temperature. The following procedure is typical: A solution of sodium phenoxide in 1,4-dioxane (125 mL) was prepared from sodium (4.5 g, 0.19 mol) and phenol (20.0 g, 0.21 mol) under an atmosphere of dry nitrogen. A solution of $\text{N}_3\text{P}_3\text{Cl}_5\text{CH}_3$ (5.0 g, 0.015 mol), dissolved in 1,4-dioxane (50 mL) was added slowly to the solution of sodium phenoxide. When the addition was complete, the reaction mixture was heated to reflux for 48 h. After this time, the reaction mixture was allowed to cool to room temperature, was poured into water (250 mL), and was extracted with diethyl ether (2 x 250 mL). The ether layer was dried over magnesium sulfate and the ether was removed under reduced pressure. This left the product contaminated with some phenol. The

excess phenol was removed by vacuum distillation (60°C/0.05 torr), to leave the crude product as an oil. The compound was purified further by filtration of a solution in CH_2Cl_2 through neutral alumina. The characterization data for the products are listed in Tables I and II.

Polymer Substitution Reactions. (a) Reactions with $\text{NaOCH}_2\text{CF}_3$. The experimental conditions found to be effective for halogen replacement in the model compound studies were also employed for substitution reactions with polymers of type VIII. The following is a typical procedure: Polymer VIII, $\{(\text{N}=\text{PCl}_2)_2-\text{N}=\text{PClR}\}_n$ (5.0 g), was dissolved in THF (200 mL) and was added dropwise over 1 h to a solution of sodium trifluoroethoxide [made from sodium (3.5 g, 0.15 mol) and trifluoroethanol (20 g, 0.20 mol) in THF (200 mL)]. When the addition was complete, the solution was heated to reflux for 48 h. After this time, the solution was allowed to cool to room temperature, was concentrated to one third of its original volume, and was poured into 2% aqueous HCl solution (1 L). The polymer which precipitated from this solution was filtered off, was dissolved in a minimum amount of THF, and was then reprecipitated into hexane (500 mL). This alternating reprecipitation into water and hexane was continued until a clear, colorless solution of the polymer in THF was obtained. A final reprecipitation into hexane was then performed and the resultant polymer was dried for 24 h in vacuo. (b) Reaction with NaOC_6H_5 . Polymer VIII, $\{(\text{N}=\text{PCl}_2)_2-\text{NPCl}(\text{CH}_3)\}_n$ (5.0 g), was dissolved in 1,4-dioxane (200 mL) and was added dropwise over 1 h to a solution of sodium phenoxide [made from sodium (4.5 g, 0.19 mol) and phenol (20.0 g, 0.21 mol) in 1,4-dioxane (200 mL)]. When the addition was complete, the solution was heated to reflux for 60 h. After this time, the solution was allowed to cool to room temperature, was concentrated to half its original volume, and was poured into 2% aqueous NaOH solution (1 L). The polymer which

precipitated from this solution was purified as described previously for the trifluoroethoxy derivatives. The characterization data for all the polymers are listed in Tables III and IV.

Acknowledgment. We thank the Office of Naval Research and the Firestone Tire and Rubber Company for the support of this work.

References and Notes

1. For a previous paper in this series see Allcock, H. R.; Fuller, T. J.; Evans, T. L. Macromolecules, 1980, submitted.
2. A preliminary communication on this work has appeared: Ritchie, R. J., Harris, P. J., Allcock, H. R. Macromolecules. 1979, 12, 1014
3. Allcock, H. R., Kugel, R. L. J. Am. Chem. Soc. 1975, 87, 4216
4. Allcock, H. R., Kugel, R. L., Valan, K. J. Inorg. Chem. 1966, 5, 1709.
5. Allcock, H. R., Kugel, R. L. Inorg. Chem. 1966, 5, 1716.
6. Allcock, H. R. "Phosphorus-Nitrogen Compounds", Academic Press, New York, 1972.
7. Allcock, H. R. Angew. Chem. 1977, 16, 147.
8. Tate, D. P. J. Polym. Sci., Polym. Symp. 1974, 48, 33.
9. Singler, R. E.; Schneider, N. S.; Hagnauer, G. L. Polym. Eng. Soc. 1975, 15,
10. Kyker, G. S.; Antkowiak, T. A. Rubber Chem. Technol. 1974, 47, 32.
11. MacCallum, J. R.; Tanner, J. J. Polym. Sci. 1968, 6, 3163.
12. Allcock, H. R.; Chu, C. T.-W. Macromolecules, 1979, 12, 551.
13. Allcock, H. R.; Patterson, D. B.; Evans, T. L. J. Am. Chem. Soc., 1977, 99
6095.
14. Allcock, H. R.; Moore, G. Y. Macromolecules, 1975, 8, 377.
15. Allcock, H. R.; Patterson, D. B. Inorg. Chem. 1977, 16, 197.
16. Allcock, H. R.; Harris, P. J. J. Am. Chem. Soc. 1979, 101, 6221.
17. Harris, P. J.; Allcock, H. R. J. Am. Chem. Soc. 1978, 100, 6512.
18. Harris, P. J.; Allcock, H. R. manuscript in preparation.
19. Kauffman, G. B.; Teter, L. A. Inorg. Synth. 1963, 7, 9.
20. Vapor phase chromatography-mass spectrometry data were obtained with the use of a Finnigan 3200 instrument fitted with a 6 ft, 3% Sp-2100 gas chromatography column.

21. Allcock, H. R. Accts. Chem. Res. 1979, 12, 351.
22. McBee, E. T.; Allcock, H. R.; Caputo, R.; Kalmus, A.; Roberts, C. W.
U.S. Govt. Astia Rep. AD 209,669 (1959).
23. Ratz, R.; Schroeder, H.; Ulrich, H.; Kober, E.; Grundmann, C. J. Am. Chem. Soc. 1962, 84, 551.
24. Fitzsimmons, B. W.; Shaw, R. A. Inorg. Synth. 1966, 8, 83.
25. Infrared data were obtained with the use of a Perkin Elmer Model 580 spectrometer.
26. Infrared spectra of KBr pellets.
27. Infrared spectra of solid films supported on NaCl windows.
28. Allcock, H. R.; Best, R. J. Can. J. Chem. 1964, 42, 447.
29. Gimblett, F. G. R. Polymer, 1960, 1, 418.
30. Konecny, J. O.; Douglas, C. M. J. J. Polym. Sci. 1959, 36, 195.
31. Konecny, J. O.; Douglas, C. M.; Gray, M. J. J. Poly. Sci. 1960, 42, 383.
32. Low resolution mass spectra were recorded on an AEI MS-902 mass spectrometer operating at 70 eV ionizing potential.
33. High resolution mass spectral data were obtained with the use of an AEI MS-902 mass spectrometer, linked to a PDP-8 computer.
34. Elemental analysis data were obtained by Galbraith Labs., Knoxville, Tennessee.
35. ³¹P NMR data were recorded on a JEOL JNM-PS-100 spectrometer operating at 40 MHz in the Fourier transform mode. The data were processed on a Nicolet 1080 computer. Peak assignments were made on the basis of ¹H decoupled and undecoupled spectra, Chemical shifts are based on the ppm scale, positive shifts are downfield from external H₃PO₄ used as a reference.
36. ¹H NMR spectra were recorded on a JEOL JNM-PS-100 spectrometer operating at 100 MHz in the Fourier transform mode. The data were processed on a Nicolet 1080 computer. Peak assignments and coupling constants were determined

on the basis of ^{31}P decoupled and undecoupled spectra. Chemical shifts are on the δ scale and referenced to internal tetramethylsilane.

37. The molecular weights were estimated by gel permeation chromatography using polystyrene standards with 10^6 , 10^5 , 10^4 , and 10^3 styragel columns in series. The solvent was tetrahydrofuran.
38. The glass transition temperatures (T_g) were measured with the use of a Chemical Instruments Corp. torsional braid analyzer, programmed to operate from -120° to $+120^\circ\text{C}$, with a temperature scan rate of $2.0^\circ\text{C min}^{-1}$.

Table I

Model Compounds. Characterization Data

<u>Compound</u>		<u>Mass spectral data</u> ³²		<u>Elemental anal.</u> ^{33,34}	
		found	calc.	found	calc.
$N_3P_3(OCH_2CF_3)_5(CH_3)$	oil	645	645	C 20.11 H 2.27 N 6.46 P 14.30	C 20.49 H 2.20 N 6.51 P 14.40
$N_3P_3(OCH_2CF_3)_5(C_2H_5)$	31	659	659	658.9969	658.9984
$N_3P_3(OCH_2CF_3)_5(n-C_3H_7)$	49	673	673	673.0156	673.0141
$N_3P_3(OCH_2CF_3)_5(n-C_4H_9)$	32	687	687	687.0286	687.0297
$N_3P_3(OCH_2CF_3)_5(i-C_3H_7)$	26	673	673	673.0144	673.0141
$N_3P_3(OCH_2CF_3)_5(t-C_4H_9)$	oil	687	687	687.0281	687.0297
$N_3P_3(OC_6H_5)_5(CH_3)$	56	615	615	C 60.50 H 4.60 N 6.80 P 15.10	C 60.53 H 4.55 N 6.82 P 15.09
$N_3P_3(OC_6H_5)_5(C_2H_5)$	84	629	629	629.1386	629.1398
$N_3P_3(OC_6H_5)_5(n-C_3H_7)$	66	643	643	643.1560	643.1554
$N_3P_3(OC_6H_5)_5(n-C_4H_9)$	oil	657	657	657.1708	657.1711
$N_3P_3(OC_6H_5)_5(i-C_3H_7)$	oil	643	643	643.1550	643.1554
$N_3P_3(OC_6H_5)_5(t-C_4H_9)$	oil	657	657	657.1701	657.1711

Table II

Model Compounds. NMR Data^a

Compound	³¹ P NMR Data (ppm) ^{35, b}		¹ H NMR Data (δ) ³⁶		Coupling Constants (Hz) ^d
	P (R) (OR')	P (OR')	R	R'	
N ₃ P ₃ (OCH ₂ CF ₃) ₅ (CH ₃)	38.3 (t)	14.3 (d)	-CH ₃	1.6 (d, t)	J _{PNP} = 47.6 J _{PCH} = 17.0 J _{PNPCH} = 2.1
			-CH ₂ CH ₃	4.2 (m)	
N ₃ P ₃ (OCH ₂ CF ₃) ₅ (C ₂ H ₅)	43.8 (t)	16.1 (d)	-CH ₂ CH ₃	1.8 (m)	J _{PNP} = 43.1 J _{PCCH} = 22.5 J _{HCCH} = 7.5
			-CH ₂ CH ₂ CH ₃	1.0 (d, t)	
N ₃ P ₃ (OCH ₂ CF ₃) ₅ (n-C ₃ H ₇)	42.1 (t)	16.0 (d)	-CH ₂ CH ₂ CH ₃	1.7 (m)	J _{PNP} = 42.9 J _{HCCH} = 7.0
			-CH ₂ CH ₂ CH ₂ CH ₃	0.9 (t)	
N ₃ P ₃ (OCH ₂ CF ₃) ₅ (n-C ₄ H ₉)	42.5 (t)	16.1 (d)	-(CH ₂) ₃ CH ₃	1.8 (m)	J _{PNP} = 43.6 J _{HCCH} = 7.2
			-(CH ₂) ₃ CH ₂ CH ₃	0.9 (t)	
N ₃ P ₃ (OCH ₂ CF ₃) ₅ (1-C ₃ H ₇)	46.7 (t)	16.5 (d)	-CH(CH ₃) ₂	1.9 (m)	J _{PNP} = 40.2 J _{PCCH} = 20.8 J _{HCCH} = 6.5
			-CH(CH ₃) ₂	1.1 (d, d)	

Table II (continued)

$N_3P_3(OC_6H_5)_5(\underline{E}-C_4H_9)$	67.3(c)	16.4(d)	$-C(\underline{CH}_3)_3$	1.2(d)	4.1(m)	J_{PNP} J_{PCCH}	= 20.1 = 21.5
$N_3P_3(OC_6H_5)_5(CH_3)$	35.9(c)	8.7(d)	$-CH_3$	1.2(d,c)	7.1(m)	J_{PNP} J_{PCH} J_{PNPCH}	= 49.2 = 17.1 = 1.2
$N_3P_3(OC_6H_5)_5(C_2H_5)$	40.1(c)	8.9(d)	$-CH_2CH_3$	1.5(m)	7.1(m)	J_{PNP} J_{PCCH} J_{HCCH}	= 43.3 = 21.5 = 7.0
$N_3P_3(OC_6H_5)_5(\underline{m}-C_3H_7)$	38.4(c)	8.7(d)	$-CH_2CH_2CH_3$	1.4(m)	7.0(m)	J_{PNP} J_{HCCH}	= 42.3 = 6.5
$N_3P_3(OC_6H_5)_5(\underline{n}-C_4H_9)$	38.7(c)	8.8(d)	$-(\underline{CH}_2)_3CH_3$	1.3(m)	7.0(m)	J_{PNP} J_{HCCH}	= 43.3 = 7.0
$N_3P_3(OC_6H_5)_5(\underline{I}-C_3H_7)$	43.3(c)	9.7(d)	$-CH(\underline{CH}_3)_2$	1.8(m)	7.1(m)	J_{PNP} J_{PCCH} J_{HCCH}	= 43.3 = 20.0 = 6.5
$N_3P_3(OC_6H_5)_5(\underline{E}-C_4H_9)$	65.5(c)	8.1(d)	$-C(\underline{CH}_3)_3$	0.95(d)	7.0(m)	J_{PNP} J_{PCCH}	= 16.7 = 21.0

a. d = doublet, t = triplet, m = unresolved multiplet. b. THF solution. c. $CDCl_3$ solution.

d. couplings unresolved if not listed.

Table III

Polymers. Characterization Data

Polymer	\bar{M}_n (GPC) ³⁷	T _g (°C) ³⁸	Elemental Analysis ³⁴			
			Found		Calcd.	
$\left[\left(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2 \right)_2 - \text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\text{CH}_3) \right]_n$	1.5×10^6	-50	C	20.40	C	20.42
			H	2.16	H	2.01
			N	6.50	N	6.48
			P	14.51	P	14.36
			F	43.51	F	44.04
			Cl	0.64	Cl	-
$\left[\left(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2 \right)_2 - \text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\text{C}_2\text{H}_5) \right]_n$	1.0×10^6	-58	C	21.75	C	21.87
			H	2.18	H	2.27
			N	6.35	N	6.37
			P	14.10	P	14.09
			F	43.17	F	43.23
			Cl	0.20	Cl	-
$\left[\left(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2 \right)_2 - \text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\text{n-C}_3\text{H}_7) \right]_n$	9.0×10^5	-55	C	23.00	C	23.20
			H	1.90	H	1.93
			N	6.24	N	6.24
			P	13.84	P	13.80
			F	42.00	F	42.34
			Cl	0.22	Cl	-
$\left[\left(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2 \right)_2 - \text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\text{n-C}_4\text{H}_9) \right]_n$	9.0×10^5	-53	C	24.36	C	24.48
			H	2.83	H	2.77
			N	6.16	N	6.11
			P	13.74	P	13.52
			F	39.47	F	41.48
			Cl	0.10	Cl	-

Table III (continued)

$\left[\text{N}=\text{P}(\text{OC}_6\text{H}_5)_2 \right]_2 - \text{N}=\text{P}(\text{OC}_6\text{H}_5)(\text{CH}_3) \Big]_n$	1.2×10^6	-15	C	60.32	C	60.52
			H	4.66	H	4.55
			N	6.71	N	6.82
			P	15.12	P	15.09
			Cl	0.05	Cl	-




Table IV


Polymer	Polymers. NMR Data ^a			
	³¹ P NMR Data (ppm) ³³		¹ H NMR Data (ppm) ³⁴	
	P(R)(OR') or P(R)Cl	P(OR') ₂ or PCl ₂	R	R'
$\left[(\text{N}=\text{PCl}_2)_2-\text{N}=\text{PCl}(\text{CH}_3) \right]_n$	10.2(m)	-21.0(m)	1.5(m)	-
$\left[(\text{N}=\text{PCl}_2)_2-\text{N}=\text{PCl}(\text{C}_2\text{H}_5) \right]_n$	17.4(m)	-19.8(m)	1.3(m)	-
$\left[(\text{N}=\text{PCl}_2)_2-\text{N}=\text{PCl}(\underline{n}\text{-C}_3\text{H}_7) \right]_n$	17.3(m)	-20.1(m)	1.2(m)	-
$\left[(\text{N}=\text{PCl}_2)_2-\text{N}=\text{PCl}(\underline{n}\text{-C}_4\text{H}_9) \right]_n$	17.3(m)	-21.3(m)	1.1(m)	-
$\left[(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2)_2-\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\text{CH}_3) \right]_n$	17.4(m)	-8.5(m)	1.5(m)	4.2(m)
$\left[(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2)_2-\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\text{C}_2\text{H}_5) \right]_n$	22.9(m)	-7.8(m)	1.4(m)	4.2(m)
$\left[(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2)_2-\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\underline{n}\text{-C}_3\text{H}_7) \right]_n$	19.3(m)	-8.2(m)	1.2(m)	4.2(m)
$\left[(\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)_2)_2-\text{N}=\text{P}(\text{OCH}_2\text{CF}_3)(\underline{n}\text{-C}_4\text{H}_9) \right]_n$	21.0(m)	-8.3(m)	1.2(m)	4.2(m)
$\left[(\text{N}=\text{P}(\text{OC}_6\text{H}_5)_2)_2-\text{N}=\text{P}(\text{OC}_6\text{H}_5)(\text{CH}_3) \right]_n$	11.0(m)	-19.1(m)	1.2(m)	7.1(m)

a. All resonance appeared as complex unresolved multiplets. No coupling constants could be determined. m = multiplet.

Legend to Figure

Representative ^{31}P NMR Spectra of Polymers X.



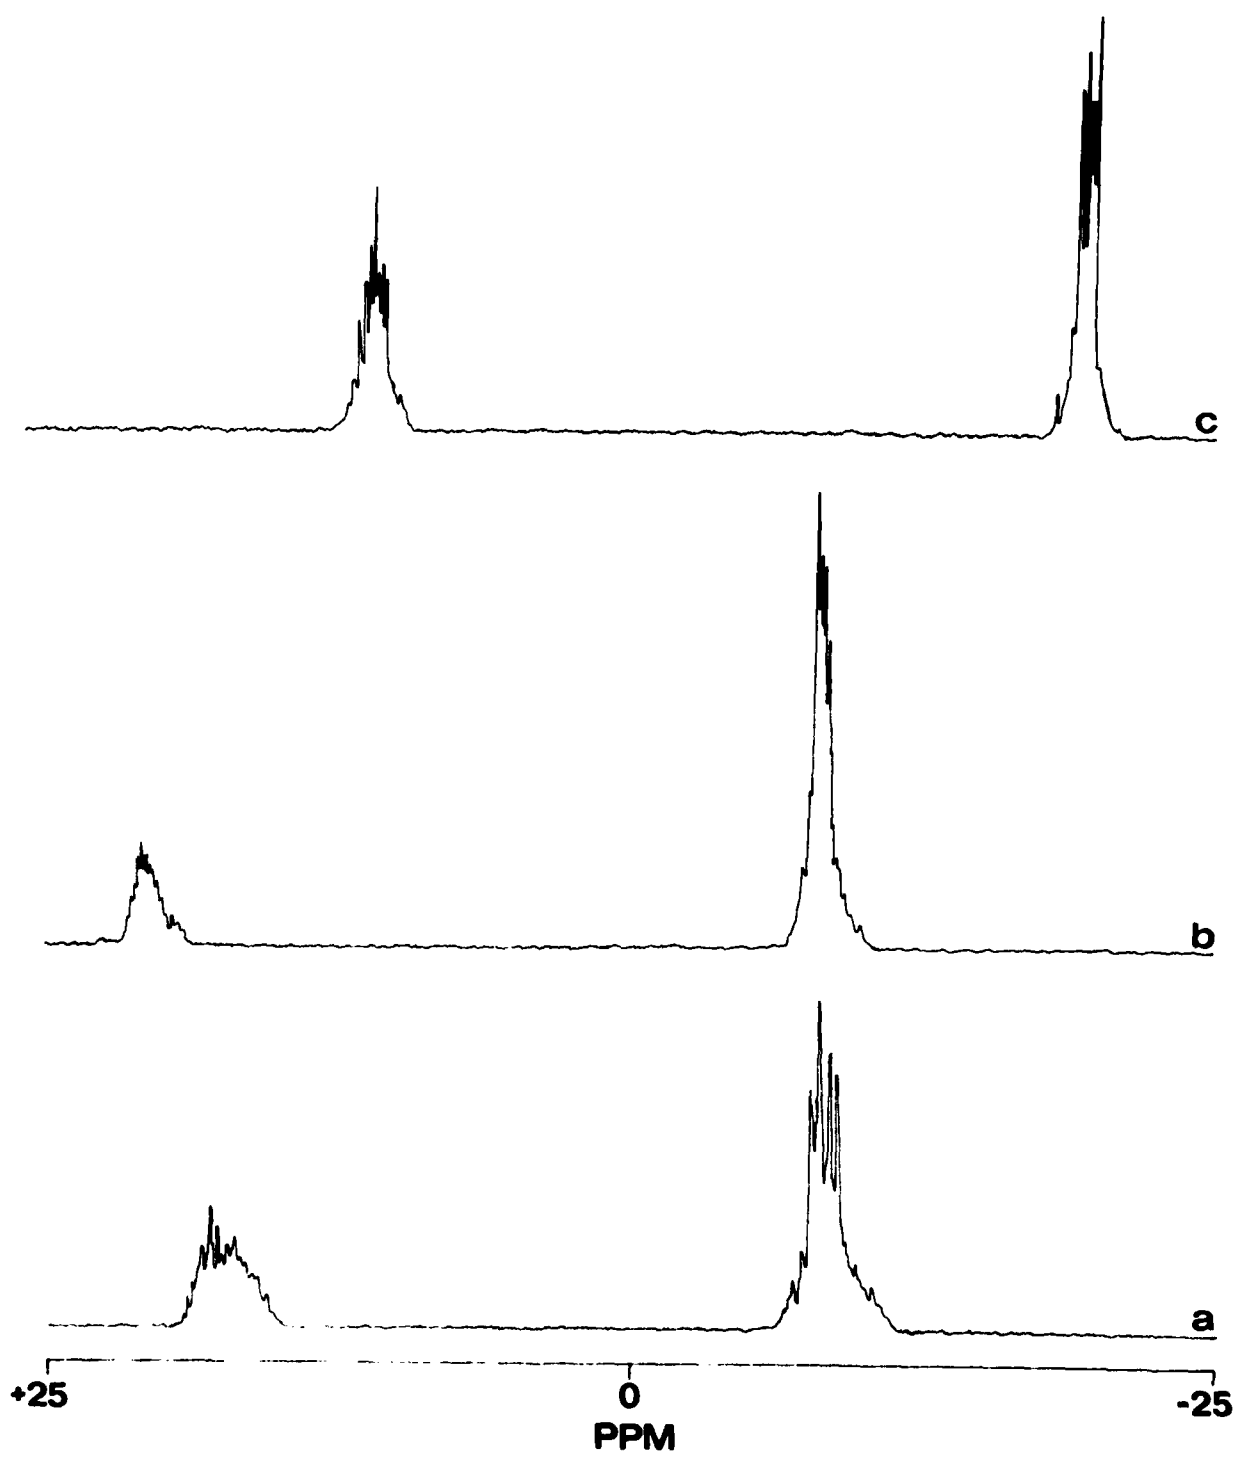

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Office of Naval Research Attn: Code 472 800 North Quincy Street Arlington, Virginia 22217	2	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 1211 Research Triangle Park, N.C. 27709	1
ONR Branch Office Attn: Dr. George Sandoz 536 S. Clark Street Chicago, Illinois 60605	1	Naval Ocean Systems Center Attn: Mr. Joe McCartney San Diego, California 92152	1
ONR Branch Office Attn: Scientific Dept. 715 Broadway New York, New York 10003	1	Naval Weapons Center Attn: Dr. A. B. Amster, Chemistry Division China Lake, California 93555	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106	1	Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	
ONR Branch Office Attn: Dr. L. H. Peebles Building 114, Section D 666 Summer Street Boston, Massachusetts 02210	1	Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
Director, Naval Research Laboratory Attn: Code 6100 Washington, D.C. 20390	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
The Assistant Secretary of the Navy (R,E&S) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1	Office of Naval Research Attn: Dr. Richard S. Miller 800 N. Quincy Street Arlington, Virginia 22217	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Department of the Navy Washington, D.C. 20360	1	Naval Ship Research and Development Center Attn: Dr. G. Bosmajian, Applied Chemistry Division Annapolis, Maryland 21401	1
Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Naval Ocean Systems Center Attn: Dr. S. Yamamoto, Marine Sciences Division San Diego, California 91232	1
Dr. Fred Saalfeld Chemistry Division Naval Research Laboratory Washington, D.C. 20375	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1

TECHNICAL REPORT DISTRIBUTION LIST, 356B

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Dr. T. C. Williams Union Carbide Corporation Chemical and Plastics Tarrytown Technical Center Tarrytown, New York	1	Douglas Aircraft Company 3855 Lakewood Boulevard Long Beach, California 90846 Attn: Technical Library C1 290/36-84 AUTO-Sutton	1
Dr. R. Soulen Contract Research Department Pennwalt Corporation 900 First Avenue King of Prussia, Pennsylvania 19406	1	NASA-Lewis Research Center 21000 Brookpark Road Cleveland, Ohio 44135 Attn: Dr. T. T. Serafini, MS 49-1	1
Dr. A. G. MacDiarmid University of Pennsylvania Department of Chemistry Philadelphia, Pennsylvania 19174	1	Dr. J. Griffith Naval Research Laboratory Chemistry Section, Code 6120 Washington, D.C. 20375	
Dr. C. Pittman University of Alabama Department of Chemistry University, Alabama 35486	1	Dr. G. Goodman Globe-Union Incorporated 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. H. Allcock Pennsylvania State University Department of Chemistry University Park, Pennsylvania 16802	1	Dr. E. Fischer, Code 2853 Naval Ship Research and Development Center Annapolis Division Annapolis, Maryland 21402	1
Dr. M. Kenney Case-Western University Department of Chemistry Cleveland, Ohio 44106	1	Dr. Martin H. Kaufman, Head Materials Research Branch (Code 4542) Naval Weapons Center China Lake, California 93555	1
Dr. R. Lenz University of Massachusetts Department of Chemistry Amherst, Massachusetts 01002	1	Dr. J. Magill University of Pittsburg Metallurgical and Materials Engineering Pittsburg, Pennsylvania 22230	1
Dr. M. David Curtis University of Michigan Department of Chemistry Ann Arbor, Michigan 48105	1	Dr. C. Allen University of Vermont Department of Chemistry Burlington, Vermont 05401	1
Dr. M. Good Division of Engineering Research Louisiana State University Baton Rouge, Louisiana 70803	1	Dr. D. Bergbreiter Texas A&M University Department of Chemistry College Station, Texas 77843	1

TECHNICAL REPORT DISTRIBUTION LIST, GEN

No.
Copies

Dr. Rudolph J. Marcus
Office of Naval Research
Scientific Liaison Group
American Embassy
APO San Francisco 96503 1

Mr. James Kelley
DTNSRDC Code 2803
Annapolis, Maryland 21402 1

TECHNICAL REPORT DISTRIBUTION LIST, 356B

	<u>No.</u> <u>Copies</u>
Professor R. Drago Department of Chemistry University of Illinois Urbana, Illinois 61801	1
Dr. F. Brinkman Chemical Stability & Corrosion Division Department of Commerce National Bureau of Standards Washington, D.C. 20234	1
Professor H. A. Titus Department of Electrical Engineering Naval Postgraduate School Monterey, California 93940	1
COL B. E. Clark, Code 100M Office of Naval Research 800 N. Quincy Street Arlington, Virginia 22217	1
Professor T. Katz Department of Chemistry Columbia University New York, New York 10027	1
Dr. Keith B. Baucom Director of Contract Research SCM-PCR Inc. P.O. Box 1466 Gainesville, Florida 32602	1