

AD-A101 653

ARMY MATERIALS AND MECHANICS RESEARCH CENTER WATERTOWN MA F/6 11/6
NOTCHED FATIGUE AND FRETTING FATIGUE LIFE OF TEXTURED TITANIUM. (U)
MAY 81 A ZARKADES

UNCLASSIFIED

AMMRC-TR-81-22

NL

1 of 1
AD-A
707083



END
DATE
FILMED
8-81
DTIC

LEVEL II



AD

AMMRC TR 81-22

AD A101653

**NOTCHED FATIGUE AND
FRETTING FATIGUE LIFE OF
TEXTURED TITANIUM**

ANTHONE ZARKADES
METALS RESEARCH DIVISION

May 1981

Approved for public release; distribution unlimited.

S DTIC
ELECTE
JUL 21 1981 **D**
D

DTIC FILE COPY

ARMY MATERIALS AND MECHANICS RESEARCH CENTER
Watertown, Massachusetts 02172

81 7 17 120

The findings in this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

Mention of any trade names or manufacturers in this report shall not be construed as advertising nor as an official indorsement or approval of such products or companies by the United States Government.

DISPOSITION INSTRUCTIONS

Destroy this report when it is no longer needed.
Do not return it to the originator.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Block No. 20

ABSTRACT

The effect of texture, (0002) poles in the transverse direction, on the notched and fretting fatigue life of a Ti-4Al-4V alloy was examined. Notched fatigue and pin-loaded flat fretting fatigue specimens were tested at room temperature in the longitudinal and transverse directions and compared to smooth bar fatigue results. Fractured fretting fatigue specimens were examined with the scanning electron microscope. Indications are that no fretting or notch fatigue anisotropy exists for the transverse type texture and specimen orientations examined. However, as expected, a significant reduction of the fatigue life is displayed for specimens subjected to fretting fatigue.

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A	

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

INTRODUCTION

The anisotropic behavior of titanium and its alloys has been investigated and reported in a state-of-the-art report.¹ One of the most important discoveries in this area has been the significant improvement and control of fatigue life with proper utilization of crystallographic preferred orientation.^{2,3} The transfusion of this research discovery could produce commercial applications which may ultimately improve helicopter reliability and efficiency.^{4,5} However, fretting, a wear phenomenon, is brought about when two contacting surfaces experience small relative movement with resultant surface interface deterioration.⁶ The process involves plastic deformation and the initiation of microcracks. The combined action of fretting and fatigue results in decreased fatigue strength and can be found in air, sea, and land vehicles and countless other engineering structures.

The National Materials Advisory Board has recommended that research studies be conducted to improve the understanding of fretting-initiated fatigue process with various material parameters including texture.⁷ Since fretting fatigue is such an obvious problem, and it has been established that crystallographic preferred orientation or texturing can affect many material properties, it was the major concern of this program to determine if any fretting fatigue-texturing relationship existed. Titanium was selected for examination because of its affinity to texturing and its increasing utilization in rotary and fixed wing design applications.

MATERIAL AND TEST PROCEDURE

The material examined was a Ti-4Al-4V nominal composition alloy in 1.5-inch-thick plate form with a hardness of 25 HRC. Tensile properties, averaged for two tests, for the longitudinal and transverse specimen orientations⁸ are given in Table 1 along with

Table 1. TENSILE PROPERTIES

Orientation	Yield Strength (psi)		Tensile Strength (psi)	Elong. (%)	E (psi)
	0.1%	0.2%			
Longitudinal	96,550	99,950	113,150	20.3	16.4 × 10 ⁶
Transverse	115,300	117,750	123,250	18.5	18.7 × 10 ⁶

CHEMICAL ANALYSES
(Weight Percent)

Al	V	O	H	N
4.18	4.11	0.134	0.007	0.018

1. LARSON, F. R., and ZARKADES, A. *Properties of Textured Titanium Alloys*. Metals and Ceramics Information Center, MCIC 74-20, June 1974.
2. ZARKADES, A., and LARSON, F. R. *Effect of Texture on Some Properties of Titanium*. Army Materials and Mechanics Research Center, AMMRC TN 73-7, May 1973.
3. SPURR, W. F., et al. *Standardization of Ti-6Al-4V Processing Conditions*. Boeing Commercial Airplane Company, AF33615-75-C-5176, December 1976.
4. LUDTKA, G. M. *HLH/ATC Titanium Alloy 6Al-4V Leading Edge Material*. Boeing Vertol Company, Report 7301-10246-1, September 1973.
5. KESSLER, H. D. *Technology Forecast*. ASM Metal Progress, v. 111, no. 1, January 1977, p. 36.
6. WATERHOUSE, R. B. *Fretting Corrosion*. Pergamon Press, New York, 1972.
7. *Control of Fretting Fatigue*. National Materials Advisory Board Committee on Control of Fretting-Initiated Fatigue, NMAB-333, 1977.
8. ZARKADES, A., and LARSON, F. R. *Effect of Texture on the Charpy Impact Energy of Some Titanium Alloy Plate*. Army Materials and Mechanics Research Center, AMMRC TR 72-21, June 1972.

the chemical analyses. Variation of other important properties with specimen orientation was reported for the same material in previous reports.^{2,8} It was established that anisotropy relative to toughness, creep stress rupture, stress corrosion cracking, and fatigue does exist. The texture is illustrated in Figure 1 and indicates a very high intensity of the (0002) poles fifteen degrees from the transverse direction.

The fretting fatigue specimen geometry was identical to that used in a Boeing-AMMRC cooperative study and simulates the fundamental and common pin-joint utilized in many structures and vehicles.⁹ The pin-loaded flat type specimen is shown in Figure 2. Specimens were machined from the rolling and transverse directions as indicated in Figure 3, and had a theoretical stress concentration factor of $K_t = 2.28$. AISI 4340 steel (40-42 HRC) shoulder screws, nominal 3/8" x 1-3/4", were utilized as pins. New pins were used with each specimen.

Notch fatigue specimen geometry with a theoretical stress concentration of $K_t = 4.50$, which is approximately twice that of the fretting sample, is shown in Figure 4. Both longitudinal and transverse specimens were tested at room temperature at a frequency of 1800 rpm and a stress ratio, $R = 0.10$.

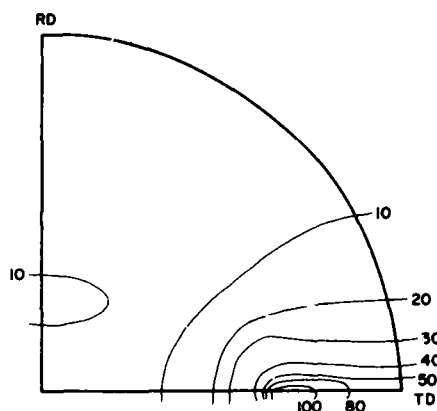


Figure 1. (0002) Pole figure of 4Al-4V-H8839.

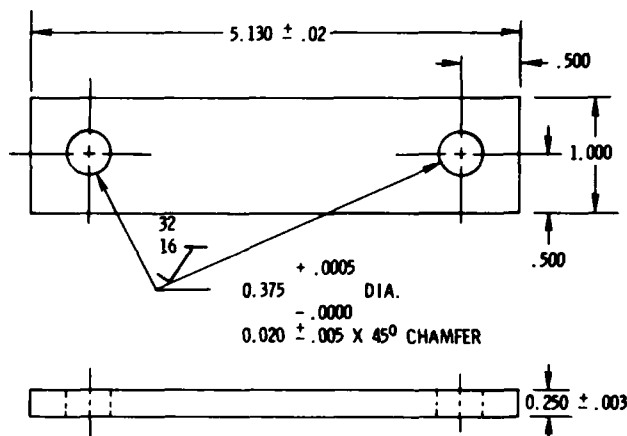


Figure 2. Pin-ended fretting fatigue specimen.

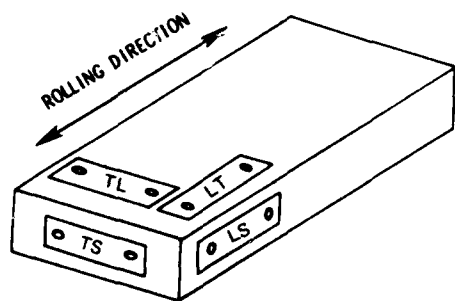


Figure 3. Schematic of specimen orientation.

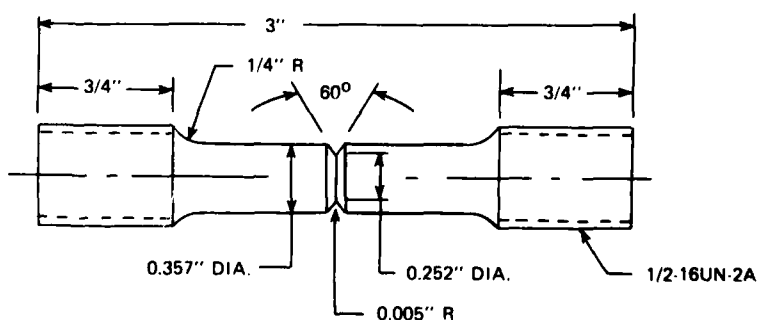


Figure 4. Notch fatigue specimen.

DISCUSSION

Fatigue results are plotted as conventional stress-cycles, S/N, curves. The transverse results, Figure 5a, show a significant decrease in fretting fatigue strength when compared to the smooth, or unfretted, strength of the material as previously reported.^{1,2} The strength reduction ranges from 55 percent at the high stress-low life area to 75 percent at 10^7 cycles. In Figure 5b the longitudinal fretting specimens show a 75 percent degradation of fatigue life along the entire curve. In fact, the reduction of fatigue life due to fretting is even more severe than that imposed by the notched specimens with twice the stress concentration. Further examination of data reveals no anisotropy with regard to LT, LS, or TS, TL orientation. The isotropic behavior of the notched and fretting fatigue life is clearly established and is especially evident when compared to the anisotropic behavior of the smooth fatigue results.^{1,2} This insensitivity of the notched and fretting fatigue life to texture indicates, as previously reported, that the effect of texture is demonstrated as an influence upon crack nucleation rather than crack propagation.

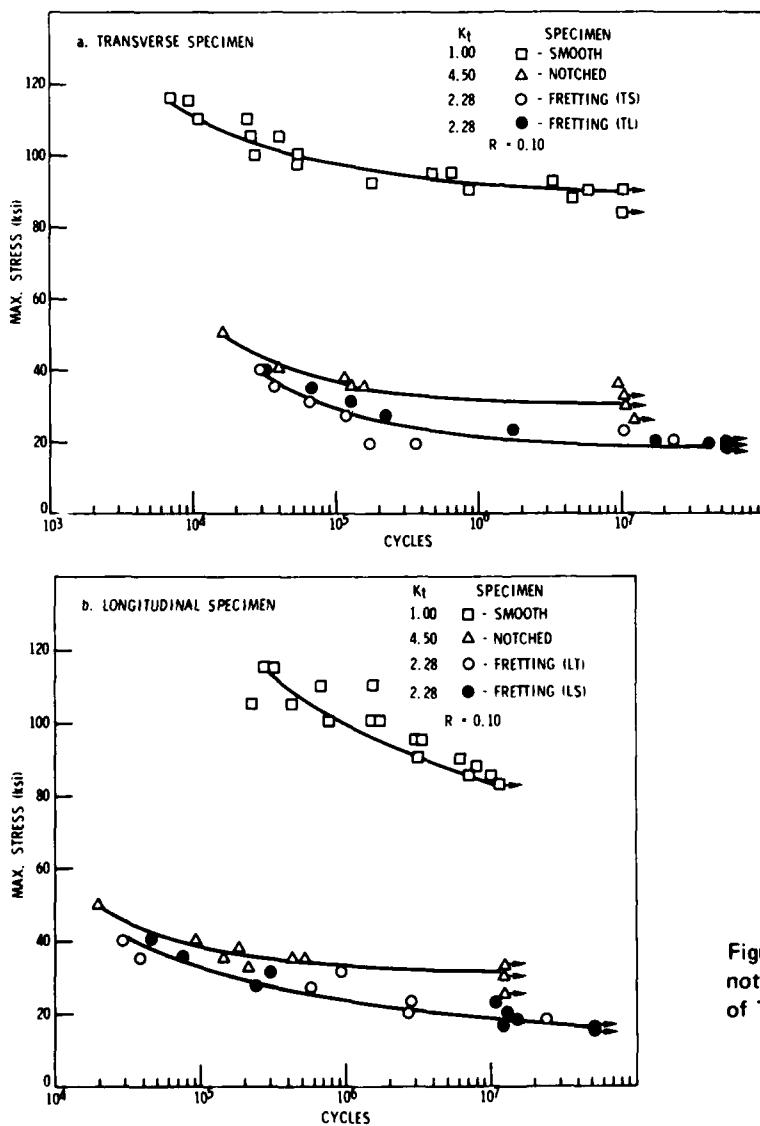


Figure 5. Comparison of fretting, notched, and smooth fatigue life of Ti-4Al-4V.

Fractured test specimens representative of those examined are shown in Figure 6a. Without exception, fracture occurred at one hole in the reduced area section. One reliable method of determining if failure is initiated by fretting is the observation of tongue and chip of the material on the fractured surface.⁶ This feature, enlarged in Figure 6b is a result of fatigue cracks which initially run obliquely to the fretting area and then continue to propagate at right angles to the stress directions.⁶

Examination of the pin, pinhole, and fracture surface was conducted on the scanning electron microscope (SEM). Fracture origin sites were found to be inside the pinhole and occur at either one site, Figure 7a, or multiple sites as in Figure 7b. Closer examination of the pinhole area revealed characteristic fretting fatigue surface damage. Cavities or scars, as shown in Figure 8, were found with fatigue cracks emanating or passing through the damaged area.

The typical condition of the steel pins taken from the fractured specimens is shown in Figure 9a. Examination of the damaged area revealed fretting debris and material in plate form as shown in Figure 9b. This exfoliation is characteristic of fretting, especially for a sphere on a flat.

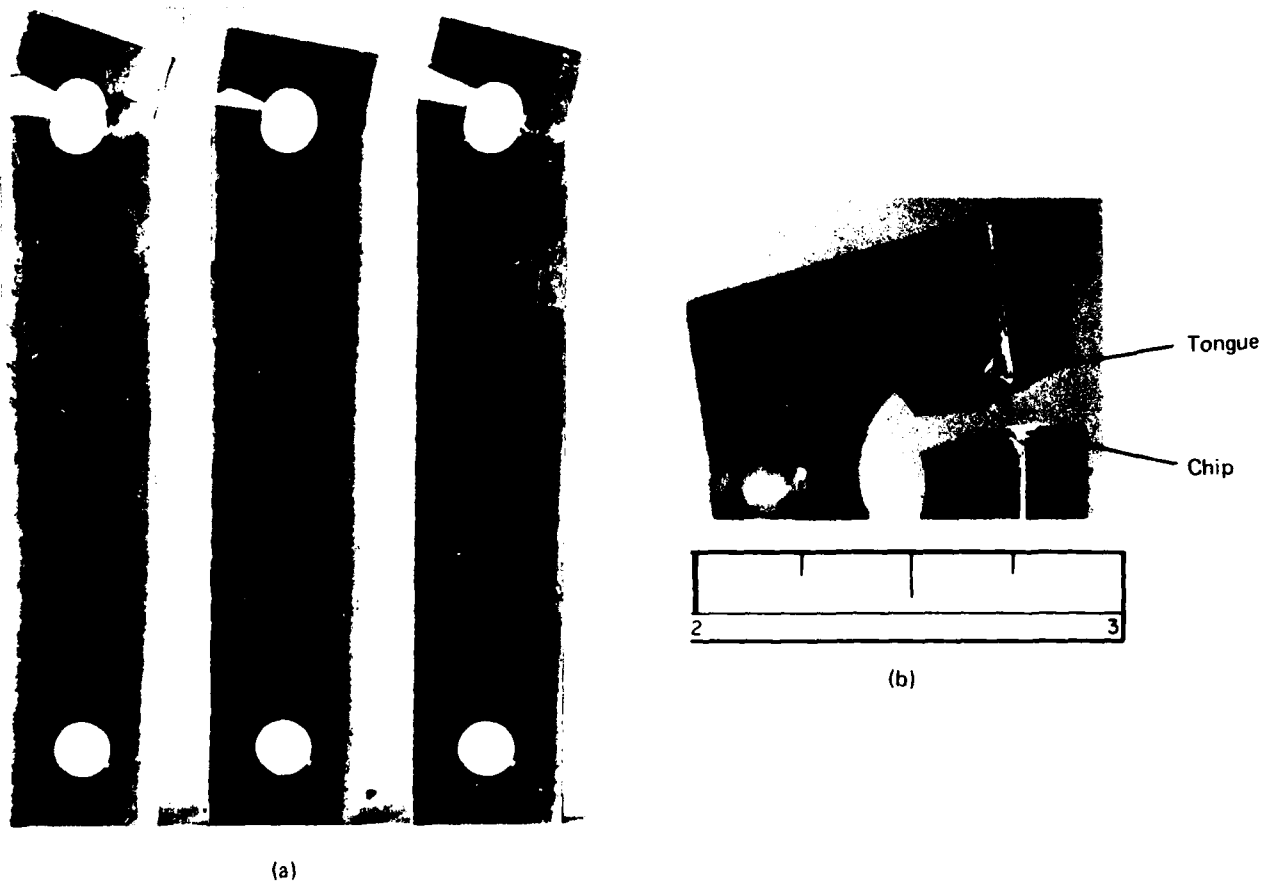


Figure 6. LT fretting fatigue specimens (a) showing enlargement of fracture surface (b).

AD
Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172
NOTCHED FATIGUE AND FRETTING FATIGUE LIFE
OF TEXTURED TITANIUM - Anthonie Zarkades

Technical Report AMMRC TR 81-22, May 1981, 8 pp -
illus-table, D/A Project IL162105AH84,
AMCMS Code 612105.H840011

AD
UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Texture
Titanium alloys
Fatigue

The effect of texture, (0002) poles in the transverse direction, on the notched and fretting fatigue life of a Ti-4Al-4V alloy was examined. Notched fatigue and pin-loaded flat fretting fatigue specimens were tested at room temperature in the longitudinal and transverse directions and compared to smooth bar fatigue results. Fractured fretting fatigue specimens were examined with the scanning electron microscope. Indications are that no fretting or notch fatigue anisotropy exists for the transverse type texture and specimen orientations examined. However, as expected, a significant reduction of the fatigue life is displayed for specimens subjected to fretting fatigue.

AD
Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172
NOTCHED FATIGUE AND FRETTING FATIGUE LIFE
OF TEXTURED TITANIUM - Anthonie Zarkades

Technical Report AMMRC TR 81-22, May 1981, 8 pp -
illus-table, D/A Project IL162105AH84,
AMCMS Code 612105.H840011

AD
UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Texture
Titanium alloys
Fatigue

The effect of texture, (0002) poles in the transverse direction, on the notched and fretting fatigue life of a Ti-4Al-4V alloy was examined. Notched fatigue and pin-loaded flat fretting fatigue specimens were tested at room temperature in the longitudinal and transverse directions and compared to smooth bar fatigue results. Fractured fretting fatigue specimens were examined with the scanning electron microscope. Indications are that no fretting or notch fatigue anisotropy exists for the transverse type texture and specimen orientations examined. However, as expected, a significant reduction of the fatigue life is displayed for specimens subjected to fretting fatigue.

AD
Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172
NOTCHED FATIGUE AND FRETTING FATIGUE LIFE
OF TEXTURED TITANIUM - Anthonie Zarkades

Technical Report AMMRC TR 81-22, May 1981, 8 pp -
illus-table, D/A Project IL162105AH84,
AMCMS Code 612105.H840011

AD
UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Texture
Titanium alloys
Fatigue

The effect of texture, (0002) poles in the transverse direction, on the notched and fretting fatigue life of a Ti-4Al-4V alloy was examined. Notched fatigue and pin-loaded flat fretting fatigue specimens were tested at room temperature in the longitudinal and transverse directions and compared to smooth bar fatigue results. Fractured fretting fatigue specimens were examined with the scanning electron microscope. Indications are that no fretting or notch fatigue anisotropy exists for the transverse type texture and specimen orientations examined. However, as expected, a significant reduction of the fatigue life is displayed for specimens subjected to fretting fatigue.

AD
Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172
NOTCHED FATIGUE AND FRETTING FATIGUE LIFE
OF TEXTURED TITANIUM - Anthonie Zarkades

Technical Report AMMRC TR 81-22, May 1981, 8 pp -
illus-table, D/A Project IL162105AH84,
AMCMS Code 612105.H840011

AD
UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Texture
Titanium alloys
Fatigue

The effect of texture, (0002) poles in the transverse direction, on the notched and fretting fatigue life of a Ti-4Al-4V alloy was examined. Notched fatigue and pin-loaded flat fretting fatigue specimens were tested at room temperature in the longitudinal and transverse directions and compared to smooth bar fatigue results. Fractured fretting fatigue specimens were examined with the scanning electron microscope. Indications are that no fretting or notch fatigue anisotropy exists for the transverse type texture and specimen orientations examined. However, as expected, a significant reduction of the fatigue life is displayed for specimens subjected to fretting fatigue.


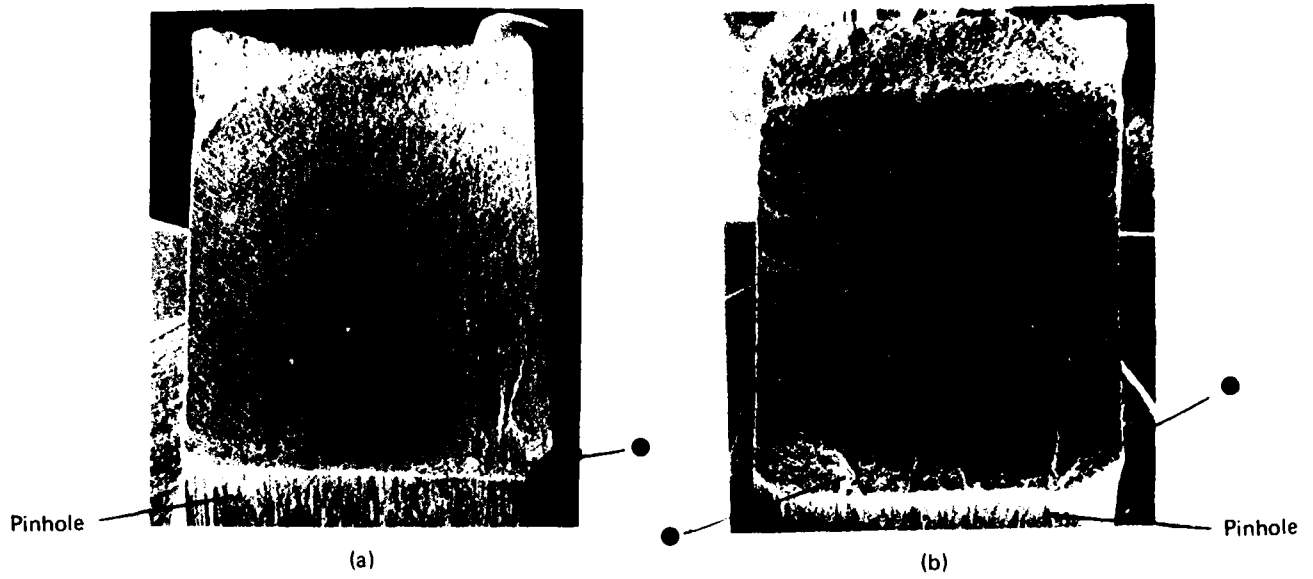


Figure 7. ● Fracture origin sites. Mag. 8.5X



a. Mag. 650X

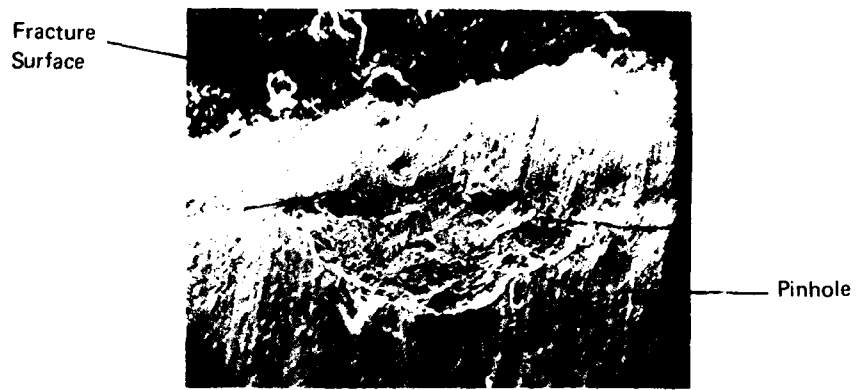

b. Mag. 1300X

Figure 8. Fatigue cracks emanating or passing through fretting damage in pinhole.

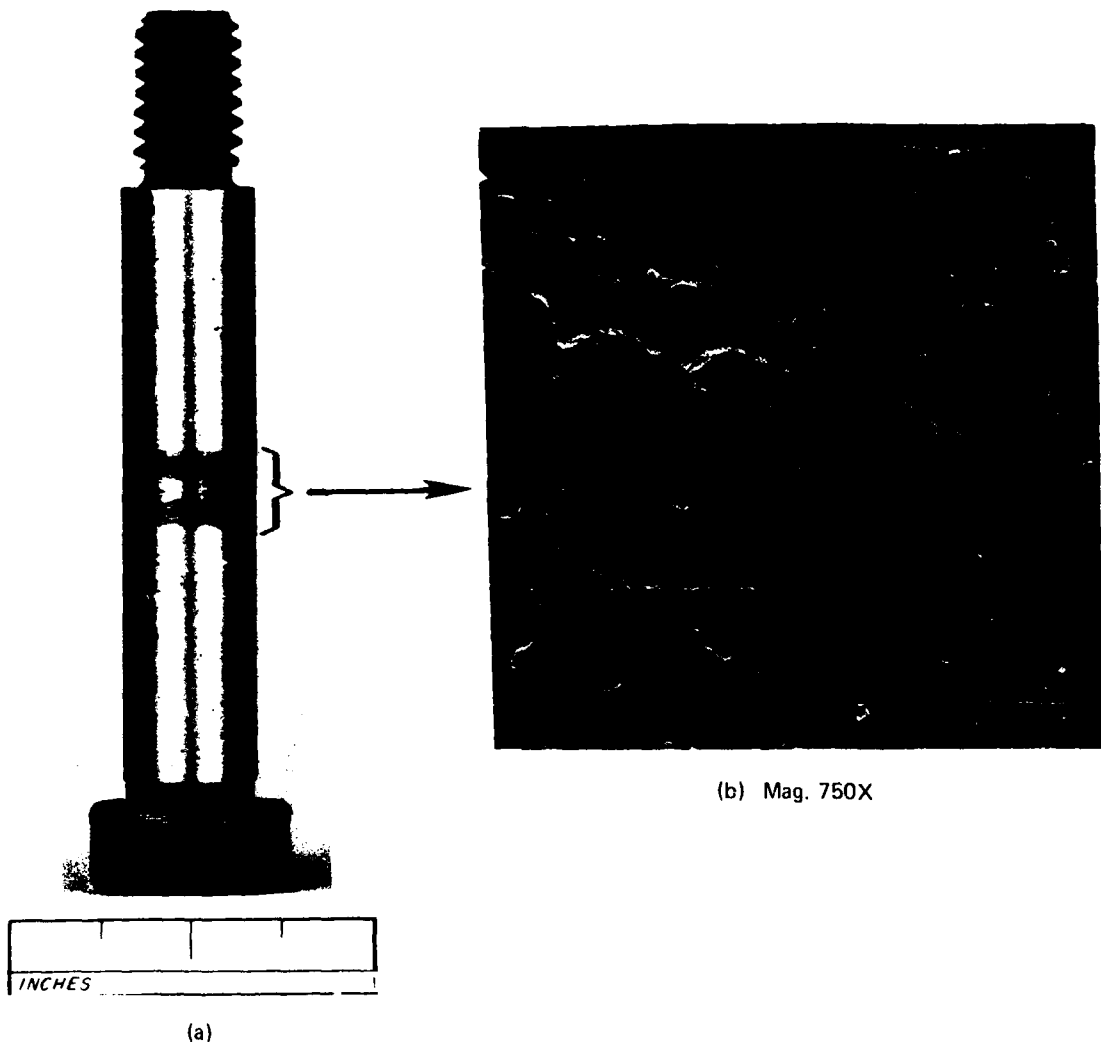


Figure 9. Steel shoulder screw pin.

CONCLUSIONS

Results have indicated that the effect of crystallographic preferred orientation on the notched specimens and fretting fatigue life is minimal. Round notched fatigue and flat titanium specimens, steel pin loaded, were tested in the longitudinal and transverse directions. No anisotropy was observed. However, comparison of fretted with unfretted samples indicated a significant strength reduction factor of four or a 75 percent reduction of the smooth fatigue life. It is clear there is a serious reduction of strength of titanium from fretting when combined with fatigue, and appropriate action needs to be taken to minimize the deleterious condition by improved design, lubrication, surface treatments, etc.

DISTRIBUTION LIST

No. of Copies	To
1	Office of the Under Secretary of Defense for Research and Engineering, The Pentagon, Washington, D. C. 20301
12	Commander, Defense Technical Information Center, Cameron Station, Building 5, 5010 Duke Street, Alexandria, Virginia 22314
1	Metals and Ceramics Information Center, Battelle Columbus Laboratories, 505 King Avenue, Columbus, Ohio 43201
	Deputy Chief of Staff, Research, Development, and Acquisition, Headquarters, Department of the Army, Washington, D. C. 20310
1	ATTN: DAMA-ARZ
	Commander, Army Research Office, P. O. Box 12211, Research Triangle Park, North Carolina 27709
1	ATTN: Information Processing Office
	Commander, U. S. Army Materiel Development and Readiness Command, 5001 Eisenhower Avenue, Alexandria, Virginia 22333
1	ATTN: DRCLDC
	Commander, U. S. Army Materiel Systems Analysis Activity, Aberdeen Proving Ground, Maryland 21005
1	ATTN: DRXSY-MP, H. Cohen
	Commander, U. S. Army Electronics Research and Development Command, Fort Monmouth, New Jersey 07703
1	ATTN: DELSD-L
1	DELS-D-E
	Commander, U. S. Army Missile Command, Redstone Arsenal, Alabama 35809
1	ATTN: DRSMI-RKP, J. Wright, Bldg. 7574
4	DRSMI-TB, Redstone Scientific Information Center
1	Technical Library
	Commander, U. S. Army Armament Research and Development Command, Dover, New Jersey 07801
2	ATTN: Technical Library
1	DRDAR-SCM, J. D. Corrie
1	DRDAR-QAC-E
1	DRDAR-LCA, Mr. Harry E. Peibly, Jr., PLASTEC, Director
	Commander, U. S. Army Natick Research and Development Command, Natick, Massachusetts 01760
1	ATTN: Technical Library
	Commander, U. S. Army Satellite Communications Agency, Fort Monmouth, New Jersey 07703
1	ATTN: Technical Document Center

No. of
Copies

To

Commander, U. S. Army Tank-Automotive Research and Development Command,
Warren, Michigan 48090
2 ATTN: DRDTA-UL, Technical Library

Commander, White Sands Missile Range, New Mexico 88002
1 ATTN: STEWS-WS-VT

Commander, Dugway Proving Ground, Dugway, Utah 84022
1 ATTN: Technical Library, Technical Information Division

Commander, Harry Diamond Laboratories, 2800 Powder Mill Road,
Adelphi, Maryland 20783
1 ATTN: Technical Information Office

Director, U. S. Army Ballistic Research Laboratory, Aberdeen Proving Ground,
Maryland 21005
1 ATTN: DRDAR-TSB-S (STINFO)

Commander, U. S. Army Foreign Science and Technology Center,
220 7th Street, N. E., Charlottesville, Virginia 22901
1 ATTN: Military Tech, Mr. Marley

Director, Eustis Directorate, U. S. Army Air Mobility Research and
Development Laboratory, Fort Eustis, Virginia 23604
1 ATTN: Mr. J. Robinson, DAVDL-E-MOS (AVRADCOM)

U. S. Army Aviation Training Library, Fort Rucker, Alabama 36360
1 ATTN: Building 5906-5907

Commander, U. S. Army Environmental Hygiene Agency, Edgewood Arsenal,
Maryland 21010
1 ATTN: Chief, Library Branch

Commandant, U. S. Army Quartermaster School, Fort Lee, Virginia 23801
1 ATTN: Quartermaster School Library

Naval Research Laboratory, Washington, D. C. 20375
1 ATTN: Dr. J. M. Krafft - Code 5830
2 Dr. G. R. Yoder - Code 6384

Chief of Naval Research, Arlington, Virginia 22217
1 ATTN: Code 471

Commander, U. S. Air Force Wright Aeronautical Laboratories, Wright-
Patterson Air Force Base, Ohio 45433
2 ATTN: AFWAL/MLSE, E. Morrissey
1 AFWAL/MLC
1 AFWAL/MLLP, D. M. Forney, Jr.
1 AFWAL/MLBC, Mr. Stanley Schulman

No. of
Copies

To

1 National Aeronautics and Space Administration, Washington, D. C. 20546
1 ATTN: Mr. B. G. Achhammer
1 Mr. G. C. Deutsch - Code RW

1 National Aeronautics and Space Administration, Marshall Space Flight
Center, Huntsville, Alabama 35812
1 ATTN: R. J. Schwinghammer, EH01, Dir, M&P Lab
1 Mr. W. A. Wilson, EH41, Bldg. 4612

1 Ship Research Committee, Maritime Transportation Research Board, National
Research Council, 2101 Constitution Ave., N. W., Washington, D. C. 20418

1 Librarian, Materials Sciences Corporation, Blue Bell Campus, Merion Towle
House, Blue Bell, Pennsylvania 19422

1 Wyman-Gordon Company, Worcester, Massachusetts 01601
1 ATTN: Technical Library

1 Lockheed-Georgia Company, 86 South Cobb Drive, Marietta, Georgia 30063
1 ATTN: Materials and Processes Engineering Dept. 71-11, Zone 54

1 General Dynamics, Convair Aerospace Division, P.O. Box 748,
Fort Worth, Texas 76101
1 ATTN: Mfg. Engineering Technical Library

1 Mechanical Properties Data Center, Belfour Stulen Inc.,
13917 W. Bay Shore Drive, Traverse City, Michigan 49684

1 Dr. Robert S. Shane, Shane Associates, Inc., 7821 Carrleigh Parkway,
Springfield, Virginia 22152

1 Mr. R. J. Zentner, EAI Corporation, 198 Thomas Johnson Drive, Suite 16,
Frederick, Maryland 21701

1 Director, Army Materials and Mechanics Research Center,
Watertown, Massachusetts 02172
2 ATTN: DRXMR-PL
1 Author