

AD-A123 911

PERMANENT MAGNET PROPERTIES OF IN SITU FORMED CU-FE  
MULTIFILAMENTARY COMPOSITES(U) HARVARD UNIV CAMBRIDGE  
DR GORDON HCKAY LAB G DUBLON ET AL. JUL 82 TR-23  
N00014-77-C-0002

1/1

UNCLASSIFIED


F/G 9/1

NL

END

FORMER

000

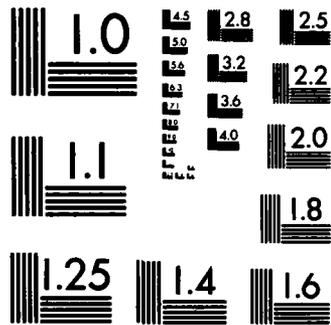

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

Office of Naval Research  
Contract N00014-77-C-0002 NR-039-136

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A	

PERMANENT MAGNET PROPERTIES OF IN SITU  
FORMED Cu-Fe MULTIFILAMENTARY COMPOSITES

By

G. Dublon, F. Habbal, and J.L. Bell



TR 23

Technical Report No. 23

This document has been approved for public release and sale; its distribution is unlimited. Reproduction in whole or in part is permitted by the U. S. Government.

July 1982

The research reported in this document was made possible through support extended the Division of Applied Sciences, Harvard University, by the Office of Naval Research, under Contract N00014-77-C-0002.

Division of Applied Sciences  
Harvard University Cambridge, Massachusetts

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 23	2. GOVT ACCESSION NO. AD-A123911	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) PERMANENT MAGNET PROPERTIES OF <u>IN SITU</u> FORMED Cu-Fe MULTIFILAMENTARY COMPOSITES	5. TYPE OF REPORT & PERIOD COVERED Interim Report	
	6. PERFORMING ORG. REPORT NUMBER	
7. AUTHOR(s) G. Dublon F. Habbal J.L. Bell	8. CONTRACT OR GRANT NUMBER(s) N00014-77-C-0002	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Division of Applied Sciences Harvard University Cambridge, Mass. 02138	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBER	
11. CONTROLLING OFFICE NAME AND ADDRESS	12. REPORT DATE July 1982	
	13. NUMBER OF PAGES 15	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) Unclassified	
	16a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report)  This document has been approved for public release and sale; its distribution is unlimited. Reproduction in whole or in part is permitted by the U. S. Government.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Permanent magnets; multifilamentary composites; high coercive force; high energy product; high strength		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Cu-Fe multifilamentary composites with up to 60 vol% Fe were prepared <u>in situ</u> . Magnetic hysteresis loops were obtained at room temperature as a function of composition, cross sectional area reduction, up to 99.9996%, and annealing conditions. $H_{ci}$ and $(B \cdot H)_{max}$ increase with cross sectional area reduction and show pronounced changes on annealing. $H_{ci} = 600, 520$ and $380$ Oe and $M_y = 5.6, 8.2$ and $11.9$ kG were measured in the smallest 30, 45 and 60 vol% Fe composites, respectively, following optimal heat treatment. $(B \cdot H)_{max} = 3.2$ MG·Oe was measured in both Cu-45 vol% Fe and Cu-60 vol% Fe with hysteresis loop squareness		

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

of 0.95. Considering the excellent mechanical and transport properties, inexpensive constituent elements and simple preparation, the in situ formed Cu-Fe composites appear to have the potential for permanent magnet applications.

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Permanent magnet properties of in situ formed Cu-Fe multifilamentary composites (a)

G. Dublon, F. Habbal, and J.L. Bell

Gordon McKay Laboratory, Harvard University, Cambridge, MA 02138 USA

ABSTRACT

Cu-Fe multifilamentary composites with up to 60 vol% Fe were prepared in situ. Magnetic hysteresis loops were obtained at room temperature as a function of composition, cross sectional area reduction, up to 99.9996%, and annealing conditions.  $H_{ci}$  and  $(B \cdot H)_{max}$  increase with cross sectional area reduction and show pronounced changes on annealing.  $H_{ci}^{\square} = 600, 520$  and  $380$  Oe and  $M_r = 5.6, 8.2$  and  $11.9$  kG were measured in the smallest 30, 45 and 60 vol% Fe (composites, respectively, following optimal heat treatment.  $(B \cdot H)_{max}^{\square} = 3.2$  MG·Oe was measured in both Cu-45 vol% Fe and Cu-60 vol% Fe) with hysteresis loop squareness of 0.95. Considering the excellent mechanical and transport properties, inexpensive constituent elements and simple preparation, the in situ formed Cu-Fe composites appear to have the potential for permanent magnet applications.

PACS numbers: 85.70.Nk, 81.20.Jz, 75.60.Ej, 75.50.Bb

INTRODUCTION

Several methods have been developed during the last decades to prepare magnetically hard metal matrix composite materials containing aligned, submicron filaments [1-7]. Recently, intrinsic coercivities,  $H_{ci}$ , of up to  $\sim 600$  Oe were measured at room temperature (RT) in in situ formed Cu-30 vol% Fe multifilamentary composites [7]. Combined with excellent mechanical [8] and transport properties [9,10] simple preparation [11] and inexpensive constituent elements, these materials appear to have the potential for permanent magnet (PM) applications. Further interest in the magnetic properties of the Cu-Fe in situ composites arises in conjunction with the extensive work on the isostructural superconducting Cu-Nb system [8-11]. The in situ formed composites with  $10^6$ - $10^{10}$  filaments/cm<sup>2</sup>, each 50-2000 Å thick and up to several mm long, have an exceptionally high dislocation density, by far exceeding the maximum attainable densities in single-phase bulk materials [8-11].

This report is concerned mostly with the practical magnetic properties of the in situ formed Cu-Fe composite system. The understanding of the unusual magnetic, mechanical and transport properties, their

interdependence and relation to the unique microstructure of the in situ composite is, however, far from complete and requires extensive additional study.

In the present work we report RT permanent magnet (PM) characteristics of in situ formed Cu-Fe composites with 30, 45 and 60 vol% Fe.

#### EXPERIMENTAL

Multifilamentary Cu-Fe composites were formed in situ following a procedure which is described in detail elsewhere [8-11]. Starting two-phase alloys were prepared by RF levitation melting of 3N Cu and Fe and rapid cooling of the liquid solution. The resulting cylindrical ingots weighing  $\sim 12$  g,  $\sim 1.2$  cm in diameter, were then vacuum annealed for 12 days at  $850^\circ\text{C}$  to partially remove Fe from solid solution and in order to facilitate plastic deformation by cold swaging. The heat treatment produces significant coarsening of the initial microstructure as illustrated in Fig. 1 for Cu-60 vol% Fe. More work on the effects of annealing on the initial microstructure (and hardness) is needed as it in turn appears to affect the PM properties of the final, multifilamentary in situ composite.

Fig. 2 shows SEM micrographs of the cross section of Cu-30 vol% Fe and Cu-60 vol% Fe wire, 250 and 180  $\mu$  in diameter, respectively, as obtained by cold swaging and drawing with intermediate anneals at 300 or  $350^\circ\text{C}$ . Samples were eventually reduced down to 25  $\mu$  in diameter or 99.9996%. The estimated average filament cross section area in the smallest composites is  $\sim 10^4 \text{ \AA}^2$ . As expected for a bcc material in an fcc matrix, the initial Fe precipitates (Fig. 1) become ribbon-like filaments (Fig. 2) with a well defined  $\langle 110 \rangle$  texture as they twist and curl due to the constraints of the surrounding matrix [8-11].

Hysteresis loops were obtained at RT using a vibrating sample magnetometer with the magnetic field applied parallel to the wire's long axis. The measurements were made as a function of composition, cold work and heat treatment ( $250\text{-}950^\circ\text{C}$ ).

#### RESULTS AND DISCUSSION

The RT saturation magnetization of the in situ formed Cu-Fe composite system increases linearly with the Fe content at 1.96 emu/g/vol% Fe between 5 and 60 vol% Fe and, within experimental accuracy, is unaffected by cold work or heat treatment beyond the first, high temperature anneal of the initial ingot. These results imply the presence of up to 2wt% Fe dissolved in the Cu matrix following the first anneal - down from  $\sim 6$  at % in the initial ingot - in agreement with

electron microprobe tests.

Figure 3 shows  $H_{ci}$  values of in situ formed Cu-45 vol% Fe composite wire at various stages of preparation. Similar results along with  $M_r/M_s$  values are shown in Fig. 4 for Cu-60 vol% Fe. Of particular interest is the dramatic increase of  $H_{ci}$  by more than a factor of 2 on proper annealing (Fig. 3). Such an increase of  $H_{ci}$  has already been reported for Cu-30 vol% Fe [7]. Similarly pronounced increases on annealing of the Young's modulus have been observed in isostructural in situ Cu-Nb composites [8]. Also, some of the increase of  $H_{ci}$  on annealing is lost by subsequent cold work (Fig. 3), resembling observed reversible changes of the elastic properties of Cu-Nb [8]. This, together with the stress dependence [10] of the superconducting properties of in situ formed Cu-Nb<sub>3</sub>Sn and Cu-Nb<sub>3</sub>Ga suggests the presence of stress induced magnetic anisotropy in Cu-Fe along with shape anisotropy. Work is in progress to determine the role of several conceivable sources of magnetic anisotropy [12] and the modes of magnetization rotation [13] in in situ formed Cu-Fe composites.

The pronounced increase, up to  $\sim 0.95$ , of both  $M_r/M_s$  (Fig. 4) and the hysteresis loop squareness with deformation and proper heat treatment implies improved filament alignment and uniformity. Anneals at high temperature (750-950°C) for only several minutes, or prolonged anneals at lower temperatures (300-500°C), produce a deterioration of the PM properties as a result of coarsening and eventual spheridization of the filaments. Some of that loss is recoverable by subsequent mechanical reduction. Additional indirect information about the composites' microgeometry is provided by the distribution of intrinsic coercivities as determined from their demagnetization remanence curves [14]. Thus obtained, the  $H_{ci}$  distributions in terms of filament volume fraction,  $v$ , for optimally annealed 30 and 60 vol% Fe samples are shown in Fig. 5. The analysis implies that  $\sim 80$  vol% of filaments possess coercivities within 25 Oe of the measured composite  $H_{ci}$  in the best PM Cu-60 vol% Fe samples (Fig. 5). Similar results were obtained for Cu-45 vol% Fe. The smallest optimally annealed Cu-30 vol% Fe composites show a much broader distribution and some of the filaments appear to have coercivities up to  $\sim 1000$  Oe (Fig. 5).

Figures 6 and 7 show RT hysteresis loops and energy product curves, respectively, of the best PM 30, 45 and 60 vol% Fe in situ composites prepared so far. The decrease of the best  $H_{ci}$  with increasing Fe content

is in agreement with general theoretical predictions [12]. However, in view of a maximum  $H_{ci}$  observed around 30 vol% Fe in powder metallurgically prepared Ag-Fe composites [2], there is work underway to determine the composition dependence of  $H_{ci}$  of in situ formed Cu-Fe down to 5 vol% Fe.

The PM properties of the Cu-Fe in situ composites (Figs. 6,7) are by far superior to those of powder metallurgically prepared composites [2-4]. In addition to their easier preparation, their PM properties are also better (Figs. 6,7) than those of conventionally prepared compacts [1]. Other structurally related materials, such as [15] Cu-1.7 wt% Fe and [16] Fe-34 at % Pd precipitation alloys as well as Au-27 at % Co aligned eutectics [5] which exhibit higher coercivities [5,15,16] have, however, much lower remanence [5,15] and/or contain very expensive constituent elements [5,16]. Overall, taking into account coercivity, remanence, maximum energy product and hysteresis loop squareness, the PM characteristics of the Cu-Fe composites (Figs. 6,7) approach the performance of Cr-Co-Cu-Fe alloys [17] and sintered [18] Cr-Co-Fe. The Cu-60 vol% Fe material with  $H_{ci}$  up to 380 Oe, high remanence and square hysteresis loop (Fig. 6) compares favorably with commercial semi-hard magnets such as Remendur and Vicalloy as well as with more recently introduced [19] Co-Fe-Nb and [6] Fe-Ni and Fe-Mn alloys. Also, considering their exceptional mechanical strength [8], high electrical [9,10] and thermal [20] conductivity, superior to those of e.g. Co-Fe-V alloys [21], the in situ formed Cu-Fe composites appear to fulfill important requirements for rotor applications.

#### SUMMARY

In situ formed Cu-Fe multifilamentary composites with 30, 45 and 60 vol% Fe exhibit a range of useful permanent magnet properties. Intrinsic coercivities of 600, 520 and 380 Oe were measured at RT in optimally annealed 35-25  $\mu$  wire with 30, 45 and 60 vol% Fe, respectively. The 45 and 60 vol% Fe composites with remanences of 11.9 and 8.2 kG, respectively, hysteresis loop squareness of 0.95 and maximum energy product of 3.2 MG $\cdot$ Oe, compare favorably with Co-based and other semi-hard magnet alloys. In view of their outstanding mechanical and transport properties, in addition to inexpensive constituent elements and relatively simple preparation, the in situ formed Cu-Fe composites appear to have the potential for a variety of permanent magnet applications.

Joze Bevk and David Turnbull are gratefully acknowledged for their help and support.

## REFERENCES

- (a) Supported in part by ONR-N00014-77-C-0002 and NSF-MRL-DMR-80-20247.
1. F.P. Levi, *J. Appl. Phys.* 31, 1469 (1960).
  2. H.P. Wahl and G. Wasserman, *Z. Metallk.* 61, 326 (1970).
  3. J.H. Swisher and E.O. Fuchs, *J. Appl. Phys.* 41, 1097 (1970).
  4. G. Frommeyer, *Metallw. Tech.* 31, 732 (1977).
  5. J.D. Livingston, *J. Appl. Phys.* 41, 197 (1970).
  6. S. Jin and T.H. Tiefel, *IEEE Trans. Mag-16*, 1062 (1980).
  7. G. Dublon, F. Habbal and J. Bevk, *Appl. Phys. Lett.* 39, 659 (1981).
  8. J. Bevk, W.A. Sunder, G. Dublon and D.E. Cohen, *Proc. MRS Conf.*, Boston, MA, Nov. 1981.
  9. K.R. Karasek and J. Bevk, *J. Appl. Phys.* 52, 1370 (1981).
  10. J. Bevk, M. Tinkham, F. Habbal, C.J. Lobb and J.P. Harbison, *IEEE Trans. Mag-17*, 235 (1981); J. Bevk and F. Habbal, *Appl. Phys. Lett.* 36, 336 (1980).
  11. J. Bevk, J.P. Harbison and J.L. Bell, *J. Appl. Phys.* 49, 6031 (1978).
  12. E.P. Wohlfarth, *Magnetism III*, eds. G.T. Rado and H. Suhl, Academic Press (New York, 1963), p. 351.
  13. S. Shtrikman and D. Treves, *ibid* p. 395.
  14. R.A. McCurrie, *Phil. Mag.* 22, 1013 (1970).
  15. A. Boltax, *Trans. AIME*, 224, 281 (1962).
  16. K. Watanabe, *Phys. Stat. Solidi (a)* 66, 697 (1981).
  17. M.L. Green, R.C. Sherwood, G.Y. Chin, J.W. Wernick and J. Bernardini, *IEEE Trans. Mag-16*, 1053 (1980).
  18. M.L. Green, R.C. Sherwood, and C.C. Wong, *J. Appl. Phys.* 53, 2398 (1982).
  19. Y. Suzuki, M. Sagawa, M. Okada and Z. Henmi, *J. Appl. Phys.* 50, 7122 (1979).
  20. F. Habbal and G. Dublon, in progress.
  21. B. Thomas, *IEEE Trans. Mag-16*, 444 (1980).

## FIGURE CAPTIONS

**Fig. 1.** SEM micrographs of polished and etched cross section of the initial Cu-60 vol% Fe ingot as cast (right) and annealed at 850°C for 12 days (left), showing the distribution of Fe precipitates (dark areas).

**Fig. 2.** SEM micrographs of the cross section of in situ formed Cu-60 vol% Fe 180  $\mu$  (right) and of Cu-30 vol% Fe 250  $\mu$  wire composite (left). The Fe filaments have been etched away (dark areas).


**Fig. 3.** Intrinsic coercivity of in situ Cu-45 vol% Fe wire composites as a function of  $\eta = \ln(a_0/a)$ , where  $a_0$  and  $a$  are the cross section areas of the initial ingot and of the composite tested, respectively. (a), (b), (c), (d) denote  $H_{ci}$  values of samples obtained by successive wire drawing (full symbols) or anneals (open symbols). The effect of intermediate anneals is indicated by type of line drawn to connect data points for both as drawn and annealed samples.

**Fig. 4.** Intrinsic coercivity and remanence to saturation ratio of in situ Cu-60 vol% Fe wire composites as a function of  $\eta = \ln(a_0/a)$ , where  $a_0$  and  $a$  are the cross section areas of the initial ingot and of the composite tested, respectively. Full lines indicate the succession of wire drawing and annealing steps taken, up to  $\eta = 12$ . Dashed and dotted lines connect  $H_{ci}$  data of samples annealed for 1 hour at 300 and 350°C, respectively.


**Fig. 5.** RT distribution of intrinsic coercivities in terms of filament volume fraction,  $v$ , as obtained from the demagnetization remanence curves of Cu-30 vol% Fe and Cu-60 vol% Fe in situ composites (see Ref. 14).

**Fig. 6.** RT hysteresis loops of optimally annealed Cu-30 vol% Fe 25  $\mu$ , Cu-45 vol% Fe 30  $\mu$  and Cu-60 vol% Fe 33  $\mu$  wire.

**Fig. 7.** RT energy product curves of the in situ Cu-Fe composites of Fig. 6.

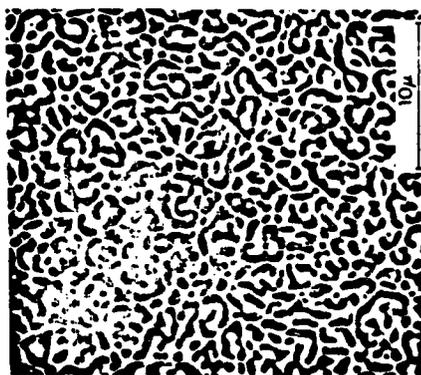

1001

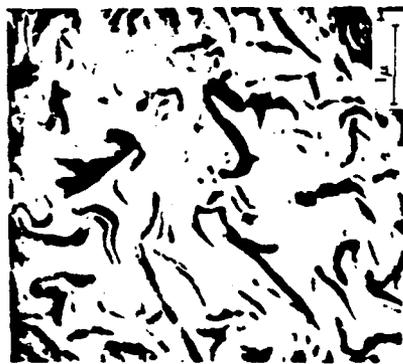

568

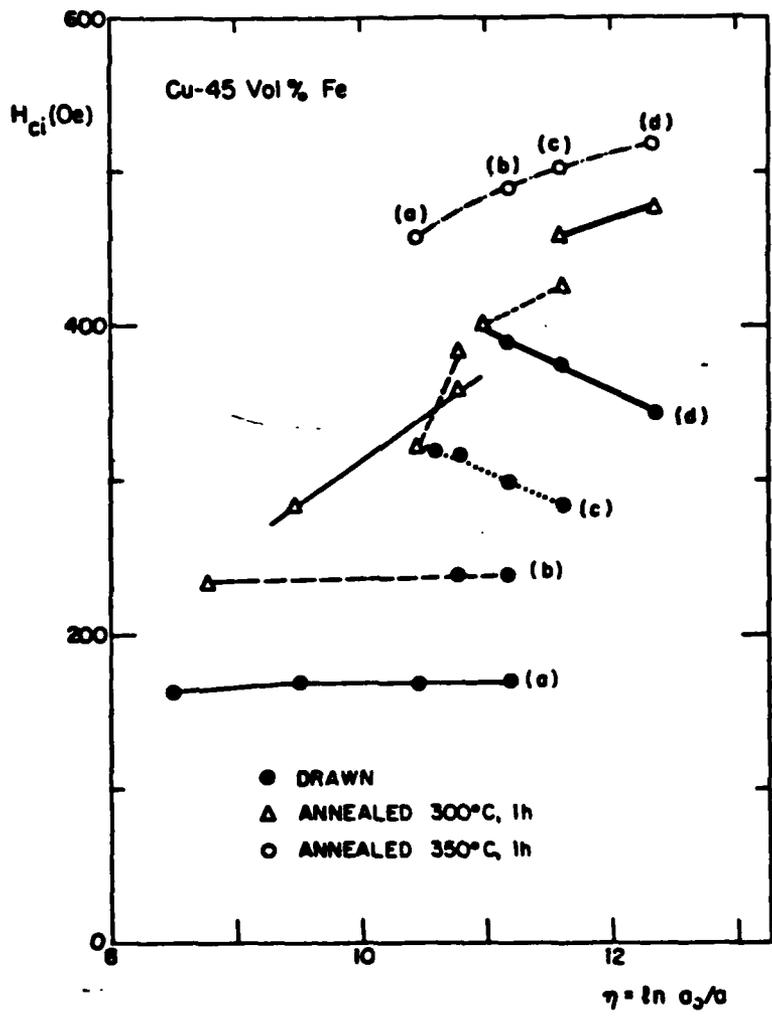


FIG. 2

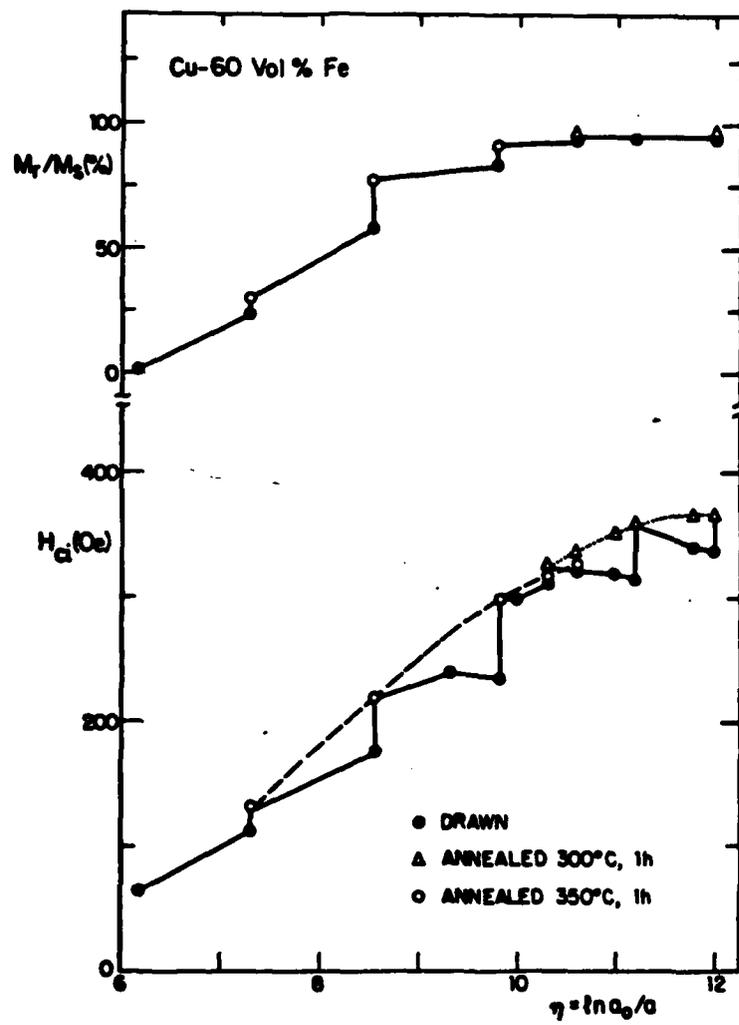


Fig. 4

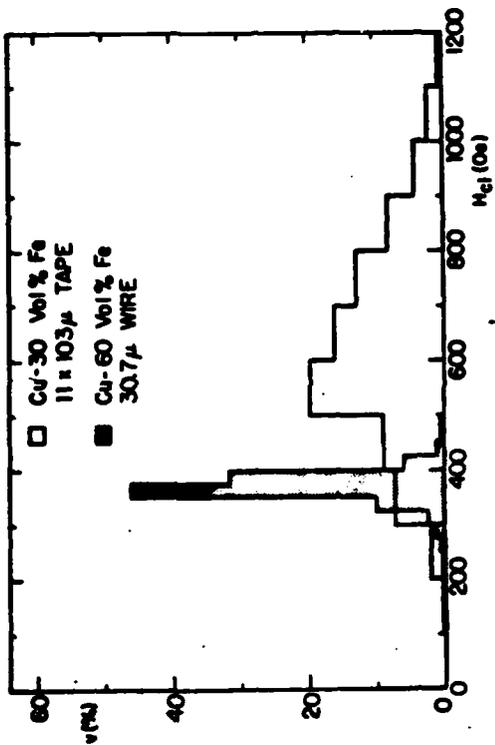


FIG. 5

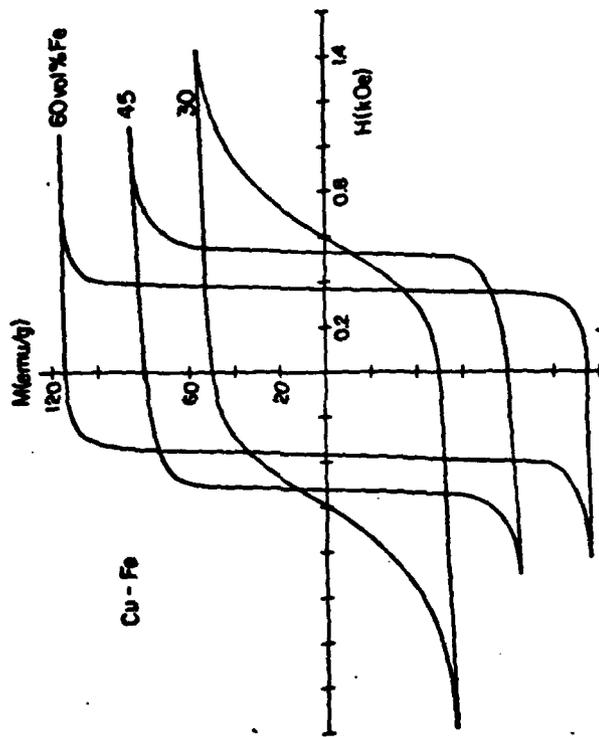


Fig. 6

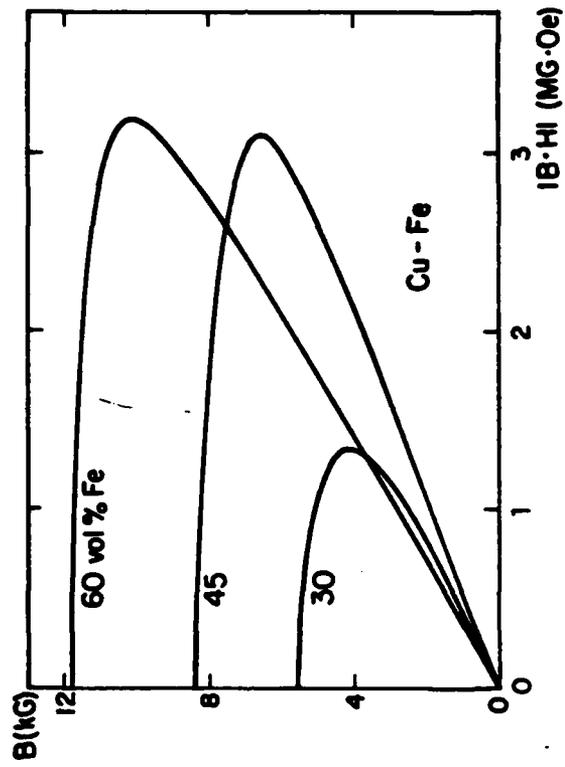


Fig. 7

Defense Documentation Center  
Georgetown Station  
Alexandria, Virginia 22304 (12)

Office of Naval Research  
Department of the Navy  
Attn: Code 471 (3)  
Code 105 (6)  
Code 470

Director  
Office of Naval Research  
Branch Office  
495 Summer Street  
Boston, Massachusetts 02210

Director  
Office of Naval Research  
Branch Office  
526 South Clark Street  
Chicago, Illinois 60605

Office of Naval Research  
San Francisco Area Office  
769 Market Street, Room 447  
San Francisco, California 94102

Naval Research Laboratory  
Washington, D. C. 20390  
Attn: Code 4500  
Code 4102  
Code 4300  
Code 6470  
Code 2427 (6)

Attn: Mr. F. S. Williams  
Naval Air Development Center  
Code 802  
Warminster, Pennsylvania 18974

Naval Air Propulsion Test Center  
Tucson, New Jersey 08620  
Attn: Library

Naval Weapons Laboratory  
 Dahlgren, Virginia 22440  
Attn: Research Division

Naval Construction Battalion  
Civil Engineering Laboratory  
Port Hueneme, California 93043  
Attn: Materials Division

Naval Electronics Laboratory Center  
San Diego, California 92162  
Attn: Electronic Materials Science Div.

Naval Missile Center  
Materials Consultant  
Code 2217-1  
Point Mugu, California 93041

Commanding Officer  
Naval Ordnance Laboratory  
White Oak  
Silver Spring, Maryland 20910  
Attn: Library

Naval Ship B. and D. Center  
Materials Department  
Annapolis, Maryland 21402

Naval Undersea Center  
San Diego, California 92132  
Attn: Library

Naval Underwater System Center  
Newport, Rhode Island 02840  
Attn: Library

Naval Weapons Center  
Chula Lake, California 93555  
Attn: Library

Naval Postgraduate School  
Monterey, California 93940  
Attn: Materials Science Dept.

Naval Air Systems Command  
Washington, D. C. 20360  
Attn: Code 52731  
Code 52732  
Code 320

Naval Sea System Command  
Washington, D. C. 20362  
Attn: Code 035

Naval Facilities  
Engineering Command  
Alexandria, Virginia 22304  
Attn: Code 03

Scientific Advisor  
Commander of the Marine Corps  
Washington, D. C. 20380  
Attn: Code AX

Naval Ship Engineering Center  
Department of the Navy  
Washington, D. C. 20350  
Attn: Director, Materials Sciences

Army Research Office  
Box 601, Duesenberg  
Durham, North Carolina 27706  
Attn: Metallurgy and Ceramics Lab

Army Materials and Mechanics  
Research Center  
Waterloo, Massachusetts 02172  
Attn: Res. Programs Office (AMM&P)

Commanding General  
Department of the Army  
Frankford Arsenal  
Philadelphia, Pennsylvania 19117  
Attn: OADBA-1910

Office of Scientific Research  
Department of the Air Force  
Washington, D. C. 20333  
Attn: Solid State Div. (SRPS)

Avcoapex Research Labs  
Wright-Patterson AFB  
Building 450  
Dayton, Ohio 45433

Air Force Materials Lab (LA)  
Wright-Patterson AFB  
Dayton, Ohio 45433

NASA Headquarters  
Washington, D. C. 20546  
Attn: Code R&M

NASA  
Lewis Research Center  
21000 Brookpark Road  
Cleveland, Ohio 44135  
Attn: Library

National Bureau of Standards  
Washington, D. C. 20234  
Attn: Metallurgy Division  
Inorganic Materials Division

Atomic Energy Commission  
Washington, D. C. 20545  
Attn: Metals and Materials Branch  
Information Center

Defense Metals and Ceramics  
Information Center  
Battelle Memorial Institute  
505 King Avenue  
Columbus, Ohio 43201

Director  
Ordinance Research Laboratory  
P. O. Box 32  
State College, Pennsylvania 16801

Director Applied Physics Lab  
University of Washington  
1013 Northeast Fort Stevens Street  
Seattle, Washington 98105

Metals and Ceramics Division  
Oak Ridge National Laboratory  
P. O. Box K  
Oak Ridge, Tennessee 37830

Los Alamos Scientific Lab.  
P. O. Box 165  
Los Alamos, New Mexico 87544  
Attn: Report Libraries

Argonne National Laboratory  
Metallurgy Division  
P. O. Box 225  
Lemont, Illinois 60439

Brockhaus National Laboratory  
Technical Information Division  
Upton, Long Island  
New York 11973  
Attn: Research Library

Library  
Building 10, Room 134  
Lawrence Radiation Laboratory  
Berkeley, California

Professor G. S. Ansell  
Researcher Polymer Institute  
Dept. of Metallurgical Engineering  
Troy, New York 12181

Professor H. Y. Brubaker  
University of Illinois  
Department of Metallurgy  
Urbana, Illinois 61801

Dr. E. M. Brennan  
United Aircraft Corporation  
United Aircraft Research Lab  
East Hartford, Connecticut 06108

Professor H. D. Brody  
University of Pittsburgh  
School of Engineering  
Pittsburgh, Pennsylvania 15213

Professor J. B. Cohen  
Northwestern University  
Dept. of Material Sciences  
Evanston, Illinois 60201

Professor M. Cohen  
Massachusetts Institute of Technology  
Department of Metallurgy  
Cambridge, Massachusetts 02139

Professor R. C. Curran  
Northwestern University  
Department of Chemistry  
Evanston, Massachusetts 02115

Dr. C. T. Meigs  
Battelle Memorial Institute  
Department of Metallurgy  
505 King Avenue  
Columbus, Ohio 43201

Professor P. W. Moore  
Carnegie-Mellon University  
Pittsburgh, Pennsylvania 15213

Dr. David C. Nowden  
Battelle Memorial Institute  
Columbus Laboratories  
105 King Avenue  
Columbus, Ohio 43201

Professor C. E. Jackson  
Ohio State University  
Dept. of Welding Engineering  
190 West 19th Avenue  
Columbus, Ohio 43210

Professor G. Judd  
Researcher Polymer Institute  
Dept. of Materials Engineering  
Troy, New York 12181

Dr. C. S. Kortovich  
TRW, Inc.  
2355 Euclid Avenue  
Cleveland, Ohio 44117

Professor D. A. Nees  
Michigan Technological University  
College of Engineering  
Houghton, Michigan 49931

Professor A. Lawley  
Drexel University  
Dept. of Metallurgical Engineering  
Philadelphia, Pennsylvania 19124

Dr. M. Margolis  
Polytechnic Institute of New York  
333 Jay Street  
Brooklyn, New York 11201

Professor K. Maschke  
Massachusetts Institute of Technology  
Department of Ocean Engineering  
Cambridge, Massachusetts 02139

Dr. G. H. Meyer  
University of Pittsburgh  
Dept. of Metallurgical and Materials  
Engineering  
Pittsburgh, Pennsylvania 15213

Professor J. W. Merris, Jr.  
University of California  
College of Engineering  
Berkeley, California 94720

Professor K. Ono  
University of California  
Materials Department  
Los Angeles, California 90024

Professor W. F. Savage  
Researcher Polymer Institute  
School of Engineering  
Troy, New York 12181

Dr. C. Shaw  
Raychem International Corp.  
P. O. Box 1503  
1049 Camino Del Rio  
Thousand Oaks, California 91320

Professor O. D. Sherby  
Stanford University  
Materials Science Dept.  
Stanford, California 94305

Professor J. Shyne  
Stanford University  
Materials Science Department  
Stanford, California 94305

Dr. W. A. Sytaig  
U.S. Steel Corporation  
Research Laboratory  
Monroeville, Pennsylvania 15146

Dr. E. A. Suther Jr.  
Massachusetts Institute of Technology  
School of Chemical Engineering  
Athens, Georgia 30332

Professor N. S. Small  
Researcher Polymer Institute  
School of Engineering  
Troy, New York 12181

Dr. E. R. Thompson  
United Aircraft Research Lab  
400 Main Street  
East Hartford, Connecticut 06108

Professor David Turnbull  
Harvard University  
Division of Engineering and Applied  
Physics  
Cambridge, Massachusetts 02139

Dr. F. W. Wang  
Naval Ordnance Laboratory  
Physics Laboratory  
Silver Spring, Maryland 20910

Dr. J. C. Williams  
Raychem International  
Science Center  
P. O. Box 1503  
Thousand Oaks, California 91320

Professor H. G. F. W. J. J. J.  
University of Virginia  
Department of Materials Science  
Charlottesville, Virginia 22903

Dr. N. A. Wright  
University of Tennessee  
Space Institute  
Dept. of Metallurgical Engineering  
Tullahoma, Tennessee 37388