

AD-A129 336

EVALUATION OF THE SHORT ROD METHOD FOR MEASURING THE
FRACTURE TOUGHNESS OF BERYLLIUM(U) TERRA TEK INC SALT
LAKE CITY UT L M BARKER ET AL. MAY 79 AMMRC-TR-79-31


1/1


UNCLASSIFIED

DAAG46-78-C-0033

F/G 11/6

NL

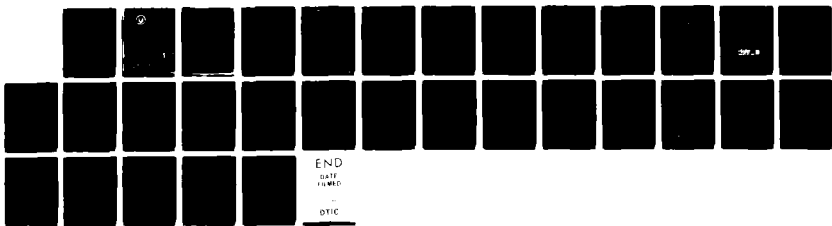

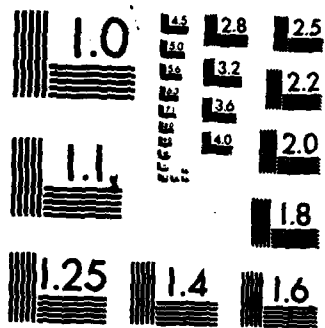

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD A129336



AD

AMMRC TR 79-31

EVALUATION OF THE SHORT ROD METHOD FOR MEASURING
THE FRACTURE TOUGHNESS OF BERYLLIUM

MAY, 1979

TERRA TEK, INC.
SALT LAKE CITY, UTAH

FINAL REPORT - CONTRACT NUMBER DAAG46-78-C-0033

Approved for public release; distribution unlimited.

DTIC
ELECTE
JUN 15 1983
S A D

FILE COPY

Prepared for

ARMY MATERIALS AND MECHANICS RESEARCH CENTER
Woburn, Massachusetts 02172

88 06 15 045

The findings in this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

Mention of any trade name or manufacturer in this report shall not be construed as endorsing or as an official endorsement or approval of such products or companies by the United States Government.

DISSEMINATION INFORMATION
Report the information in this report unless
otherwise indicated.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER AMMRC TR 79-31	2. GOVT ACCESSION NO. AD-A129336	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Evaluation of the Short Rod Method for Measuring the Fracture Toughness of Beryllium	5. TYPE OF REPORT & PERIOD COVERED Final Report	
7. AUTHOR(s) L.M. Barker R.V. Guest	6. CONTRACT OR GRANT NUMBER(s) DAAG46-78-C-0033	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Terra Tek, Inc. Salt Lake City, UT 84108	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS D/A Project: 8X3633304D215 AMCMS Code: 633304.21500.03 Agency Accession:	
11. CONTROLLING OFFICE NAME AND ADDRESS Army Materials and Mechanics Research Center Watertown, Massachusetts 02172	12. REPORT DATE May 1979	13. NUMBER OF PAGES 25
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) Unclassified	
15a. DECLASSIFICATION/DOWNGRADING SCHEDULE		
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Beryllium Fracture tests Fracture strength Mechanical tests Stresses		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The fracture toughness of CIP/HIP-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 method except for using K_f in fatigue pre-cracking of about $0.8 K_{Ic}$ as opposed to the $0.6 K_{Ic}$ required by E 399 (beryllium is very difficult to fatigue pre-crack). The CT measurements agreed very well with previous measurements of the toughness of beryllium. The tested CT specimen halves were then machined into short rod specimens, and the fracture toughness was measured by the		

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Block No. 20

ABSTRACT

short rod method. The average of the short rod measurements differed from the average CT measurement by about 2 percent. In addition, the short rod tests provided a measure of K_{Ia} , the stress intensity factor which allows a fast-moving crack to arrest. These results, together with the simplicity of the short rod test in which no fatigue pre-cracking is required, make the short rod method attractive for measuring the fracture toughness of beryllium.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

FOREWORD

This study has been conducted by Terra Tek, Inc., Salt Lake City, Utah, under contract No. DAAG 46-78-C-0033 from the Army Materials and Mechanics Research Center, Watertown, MA. Mr. J. F. Dignam of the AMMRC was project manager, and Dr. S. C. Chou of the AMMRC served as technical monitor. The advice and guidance of Mr. Dignam and Dr. Chou in this study are much appreciated.

Accession For	
NEWS GRA&I	<input checked="" type="checkbox"/>
DOC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A	



ABSTRACT

The fracture toughness of CIP/HIP-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 method except for using K_F in fatigue pre-cracking of about $0.8 K_{IC}$ as opposed to the $0.6 K_{IC}$ required by E 399 (beryllium is very difficult to fatigue pre-crack). The CT measurements agreed very well with previous measurements of the toughness of beryllium. The tested CT specimen halves were then machined into short rod specimens, and the fracture toughness was measured by the short rod method. The average of the short rod measurements differed from the average CT measurement by about 2 percent. In addition, the short rod tests provided a measure of K_{Ia} , the stress intensity factor which allows a fast-moving crack to arrest. These results, together with the simplicity of the short rod test in which no fatigue pre-cracking is required, make the short rod method attractive for measuring the fracture toughness of beryllium.

TABLE OF CONTENTS

	Page
Foreword	i
Abstract	ii
Table of Contents	iii
List of Figures	iv
Introduction	1
Experimental	3
Short Rod Data Reduction	8
Results and Discussion	11
Summary	13
References	14

LIST OF FIGURES

<u>Figure No.</u>	<u>Description</u>	<u>Page</u>
1	Short rod specimen with crack denoted by the shaded area	2
2	Photograph of the fractured surfaces of the beryllium compact toughness specimens	3
3	Dimensions of the beryllium short rod specimen	4
4	Typical load-displacement record for an LFM short rod fracture toughness specimen. The solid line is the actual test record; the broken line is the standard curve model	6
5	Load-displacement record for beryllium sample #3-2. The broken line is the standard curve model least squares fit to the top portion of the test record	6

INTRODUCTION

Beryllium is an important aerospace material because of its light weight, high modulus, and high heat capacity, coupled with good strength. It is a brittle material, however, and hence its fracture toughness is of concern. Although beryllium fracture toughness measurements have been made by a number of investigators^{1,2}, there is considerable scatter among the results obtained. The main difficulty in the fracture toughness testing has been obtaining a real crack in the test specimen, and this has led in some cases to the use of machined notches rather than real cracks. Attempts at fatigue pre-cracking according to ASTM E 399-74³ have been largely unsuccessful or have proved quite expensive because of the extremely slow fatigue crack growth rate at crack tip loadings of no more than $0.6 K_{Ic}$. A subcommittee of the ASTM is currently attempting to standardize a new test procedure which would be especially adapted to, and limited to, beryllium.⁴

The recently developed short rod method of measuring fracture toughness^{5,6} has been successfully applied to a number of very brittle materials, including fused quartz, ceramics and cemented carbides. One of the main advantages of the short rod specimen (Figure 1) is that the necessary pre-crack is created automatically during the test without any fatigue cycling, even in the most brittle materials. It therefore appeared that the short rod method might be ideal for rapid, economical tests of the plane-strain fracture toughness of beryllium.

This paper reports the results of a test series on beryllium whose objective was to compare critical stress intensity factors measured by the short rod method with those obtained by essentially the method of E 399-74.³ The test series provided not only the desired toughness measurement comparison, which was very good, but also gave a measure of the stress intensity factor at the time of crack arrest of a rapidly moving crack in beryllium.

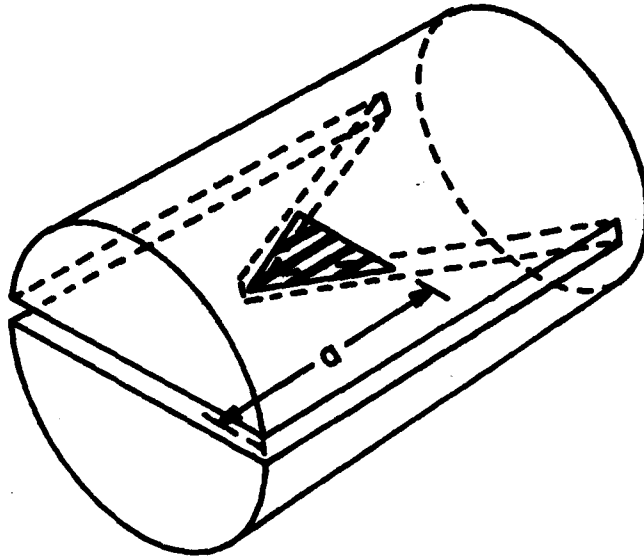


Figure 1. Short rod specimen with crack denoted by the shaded area.

EXPERIMENTAL

The material used for these tests was Kawecki Berylco CIP/HIP-1 beryllium. Its density was 1.852 g/cm³; its grain size was from 8 to 9 microns. Its elemental analysis was as follows (in parts per million):

BeO	Fe	Al	Mg	Si	C	Cr	Co	Cu	Pb	Mn	Mo	Ni
1.09×10^4	200	40	35	83	203	24	25	40	1	13	<10	125

Five compact toughness (CT) specimens were machined from the beryllium and tested according to ASTM E 399-74, with the exception that the K_F used in fatigue was approximately 0.8 K_Q , and reversed loading ($R = -2$ to -3) was also used. These deviations from E 399-74 coincide with recommendations made by ASTM Task Group E24.01.11 on Fracture Testing of Beryllium.⁴ The CT specimens were 15.9 mm thick, and had a W/B ratio³ of 2. Figure 2 shows the tested specimen halves. The fatigue pre-cracked areas show as darker regions in the figure.

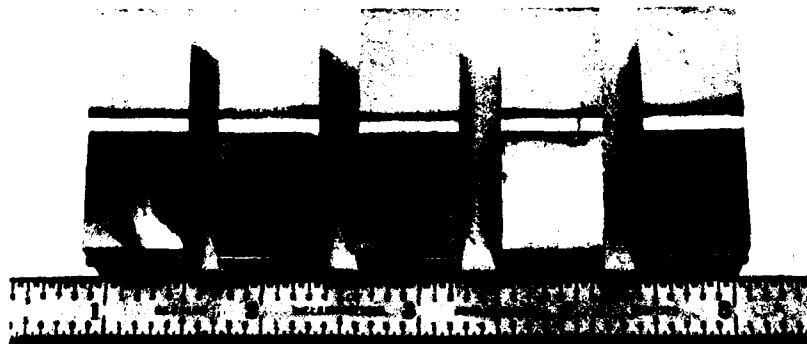


Figure 2. Photograph of the fractured surface of the beryllium compact toughness specimens.

After the five CT specimens were tested, a short rod fracture toughness specimen was machined from each of the ten CT specimen halves. The short rods and their slots were oriented such that the crack plane in the short rod would be parallel to the crack plane in the parent CT specimen. The short rod specimen dimensions are given in Figure 3. The slots which form the "V" in the specimen were 0.38 mm thick, and had curved bases because they were sawed by letting the specimen down onto a circular saw blade. For ease of measurement, the angle of the "V" was defined as the chord angle, as illustrated in Figure 3.

The short rods were tested using the Terra Tek Fractometer I,⁶ a machine especially designed for testing short rod and short bar specimens of hard, brittle materials. Briefly, a fracture toughness test normally consists of inserting a very thin inflatable stainless steel bladder, called a "flatjack", into the slot in the front face of the specimen. The flatjack extends 6.12 mm into the slot, almost to the point of the V. The flatjack is then inflated with a high-modulus fluid (mercury), and contacts the inner walls of the slot. Further inflation then increases the pressure in the flatjack, thus imparting a distributed opening load in the specimen mouth.

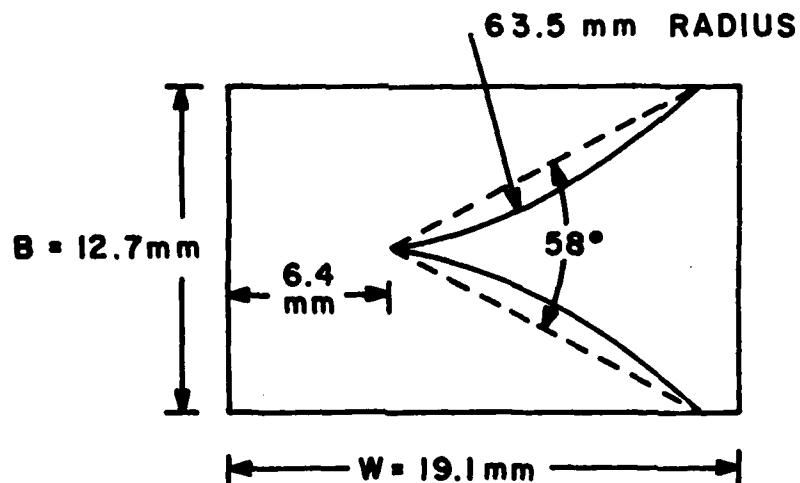


Figure 3. Dimensions of the beryllium short rod specimens.

The opening load causes a stress concentration at the point of the V in the specimen, such that a fracture first initiates there. Normally, the crack is initially quite stable because of the constant widening of the crack front as it propagates. Thus, an ever-increasing load is required initially to keep the crack moving. When the crack reaches a certain critical length, a_c , (about where it is shown in Figure 1), the crack-advancing load normally goes through a smooth maximum, and thereafter it decreases with further crack growth. It is found both experimentally and theoretically^{5,6} that the crack length, a_c , at peak load is a constant for a given specimen configuration, independent of the specimen material, provided the specimen obeys the principles of linear elastic fracture mechanics (LEFM). Thus, the peak load in a short rod test is the load required to advance the crack when the crack length is a_c , and therefore, the peak load can be shown to be directly proportional to the critical stress intensity factor. In the case of flatjack loading of the short rod specimen, the fracture toughness is given by⁶

$$K_{IC} = A_F P_C \sqrt{B} , \quad (1)$$

where P_C is the peak pressure in the flatjack during the test, B is the specimen diameter, and A_F is a dimensionless constant so long as the scaled specimen geometry remains constant. The value of A_F used for the short rod specimen geometry of this study (Figure 3) was

$$A_F = 8.26 \quad (2)$$

Although many short rod tests of fracture toughness are done as described above without making any plot of load vs. specimen mouth opening displacement, such plots can often be of value for detecting rate effects, stress corrosion cracking, abnormalities in apparent toughness along the crack path, etc. They can also be used to determine whether the specimen obeys the assumptions of linear elastic fracture mechanics, provided at least one relaxation of the load is done when the crack is in the vicinity of the critical crack length. Figure 4 shows a typical load-displacement record for a fracture toughness test of tungsten carbide/cobalt.

Load-displacement test records were made of each of the ten beryllium short rod specimens in order to extract the maximum information from the tests. Instead of smooth records like that of Figure 4, however, the beryllium load-displacement records all had the general appearance shown in Figure 5,

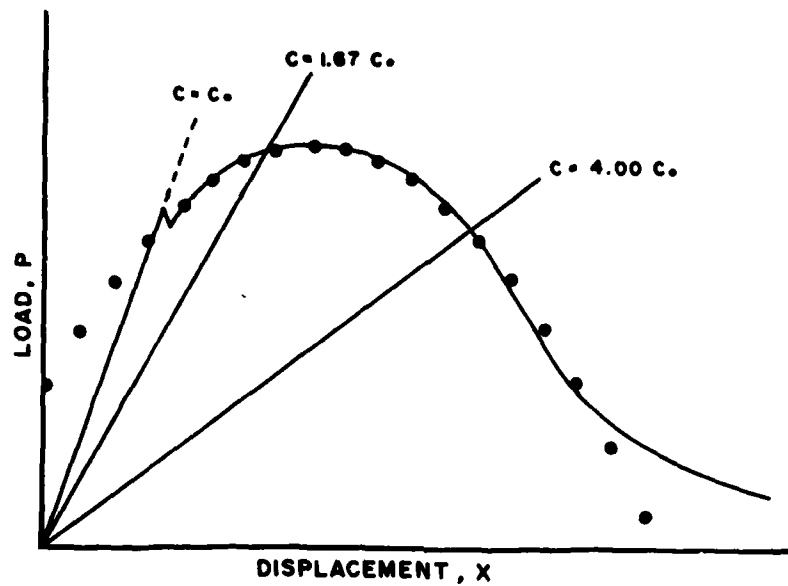


Figure 4. Typical load-displacement record for an LEFM short rod fracture toughness specimen. The solid line is the actual test record; the broken line is the standard curve model.

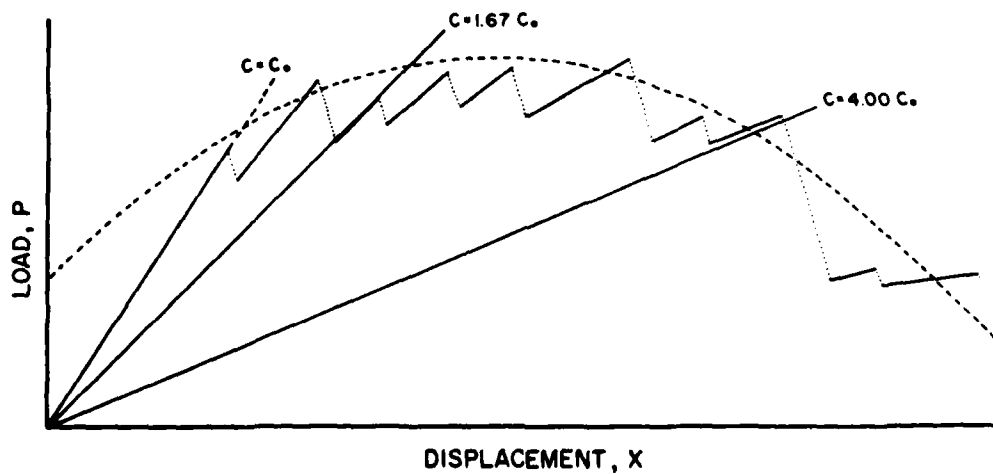


Figure 5. Load-displacement record for beryllium sample #3-2. The broken line is the standard curve model least squares fit to the top portion of the test record.

which is the plot of one of the tests. Although the loading was done smoothly and continuously, the crack would remain almost stationary until it would suddenly jump ahead, producing the audible "tick", a sudden decrease in load, and an increase in the specimen mouth opening. The crack would then remain almost stationary again until the next jump ahead, thus producing records like that of Figure 5. Although the Fractometer load-displacement plots at first appeared discouraging, they actually provided much more than the usual single critical stress intensity factor which allows a fast-moving crack to arrest. The data interpretation and data reduction procedures used for the beryllium data are discussed in the next section.

SHORT ROD DATA REDUCTION

In a normal LEFM short rod test, it is clear that the stress intensity factor at the crack tip is constantly at its critical value during the period of slow, steady-state crack growth. Thus, in a test record such as that of Figure 4, all points significantly beyond the initial linear elastic loading portion of the load-displacement path correspond to K_{IC} conditions at the crack front. Any one of those points could be translated into a K_{IC} measurement if the corresponding crack length and compliance derivative were known. It is convenient, of course, to use the peak load point on the load-displacement path to calculate K_{IC} , because the dimensionless crack length, a_c/B , and the compliance derivative, $d[(cEB)/d(a/B)]_{ac}/B$ are always the same at that point, regardless of the specimen material. These quantities are contained in the short rod calibration constant, A_F (cf. Eq. 1 and 2).⁶

In the tests of beryllium, however, very few of the points on the load-displacement path correspond to K_{IC} conditions at the crack tip, because significant crack growth initiated only at those points where crack jumps began. It was reasoned that if beryllium had not displayed the crack jump behavior (which is caused by the dynamic toughness, K_{Id} , being smaller than K_{IC}), the load-displacement record would have been smooth, and would have passed through the points on the observed record where crack jumps initiated. Thus, if one could use the crack jump initiation points to reconstruct a smooth load-displacement record, the peak load on that record could be used in Equation 1 to calculate K_{IC} .

A theoretical investigation showed that for a given scaled short rod specimen geometry, all normal LEFM load-displacement records such as that of Figure 4 can in principle be scaled to a single, standard load-displacement curve. Further, if the standard curve were known, any single K_{IC} point on an actual load-displacement plot could be used to reconstruct the rest of the curve, complete with the P_c point from which K_{IC} can be calculated.

Therefore, for reducing the beryllium data, a mathematical model of the standard LEFM load-displacement curve was derived. The relation, which adequately describes a substantial portion of the normal LEFM test record, is the quadratic

$$(1-s)P_c^2 - (P + \frac{2rs}{c_0} x) P_c + \frac{r^2s}{c_0^2} x^2 = 0, \quad (3)$$

where P_c is the peak load on the curve, P and x are the load and displacement at any point on the curve, c_0 is the initial elastic loading compliance of the specimen as measured from the load-displacement test record, and r and s are dimensionless constants whose values for the specimens of this study, as determined by fitting Equation 3 to several normal LFM experimental curves, are approximately

$$\begin{aligned} r &= 0.50 \\ s &= -0.60 \end{aligned} \quad (4)$$

Equation 3 is written in the form of a quadratic in P_c , and assumes that the origin of the P, x coordinates is at the start of the initial linear elastic loading path. The coefficients of P_c for any given crack jump initiation point are determined from the values of r and s (Equation 4), from the (P, x) coordinates of the crack jump initiation point, and from the initial elastic compliance,

$$c_0 = \frac{\Delta x}{\Delta P}, \quad (5)$$

evaluated along the slope of the initial loading path on the test record. Hence, the evaluation of the fracture toughness of a beryllium specimen from its short rod load-displacement curve was practicable. First, for a particular test record, such as that of Figure 5, the value of P_c in Equation 3 was found for one crack jump initiation point (P, x) . The value of P_c was used in Equation 1 to find the value of K_{IC} for that point. This procedure was repeated for several crack initiation points on each load-displacement record. The average of the K_{IC} values obtained in this way from each specimen is reported in Table 1.

Since nonplane strain effects on the crack are more pronounced in the initial region and in the final region of crack growth, the load-displacement points used to evaluate the fracture toughness should correspond to crack lengths of intermediate size. Because the compliance of a specimen is related to its crack length, the compliance at a P, x data point in question, taken as $c = x/P$, was used to judge the acceptability of the point in calculating the

toughness. Data points in the compliance range $1.67c_0 < x/P < 4.00 c_0$ were taken as acceptable for this study. The values of r and s (Equation 4) were selected to produce a good match of several experimental normal LFM curves over this compliance range. Figure 4 shows the compliance range and the fit of Equation 3 to one of the normal LFM records used to evaluate r and s .

Just as the load-displacement points at which crack jumps initiated correspond to K_{Ic} data points, the load-displacement points at which crack arrest occurred correspond to the stress intensity factor which allows a fast-moving crack to arrest, K_{Ia} . By using crack arrest points in the above procedure, several values of K_{Ia} were also obtained from each test record.

RESULTS AND DISCUSSION

Table 1 presents a summary of the beryllium fracture toughness data obtained from the CT and the short rod specimens, including the K_{Ia} values obtained from the short rod tests. Although the CT tests did not meet the ASTM fatigue pre-cracking requirement, the toughness values are listed as K_{IC} values, inasmuch as an ASTM task group has recommended relaxing the fatigue pre-cracking requirement for beryllium.⁴

The average of the five CT toughness values for the beryllium of this study is $10.40 \text{ MPa}\sqrt{\text{m}}$, with a standard deviation of 4.5 percent. The average toughness for the ten short rod beryllium specimens was only 2.3 percent higher, $10.63 \text{ MPa}\sqrt{\text{m}}$, with a standard deviation of 3.0 percent. These results agree with the values of fracture toughness reported by Conrad, *et. al.*,⁴ for a similar beryllium pressing as measured by several laboratories for a round robin test program conducted for NASA-Lewis. The average of their values was $10.37 \text{ MPa}\sqrt{\text{m}}$, with a standard deviation of 7 percent. Apparently, part of the scatter in the reported data is due to lab-to-lab variations, since the average standard deviation reported by each individual laboratory participating in the study was only 5.5 percent.

It is interesting to compare the standard deviation of the CT tests to the standard deviation of the short rod tests performed for this study. The improved standard deviation in the short rod tests is undoubtedly due to the averaging of several K_{IC} values in obtaining the K_{IC} for each short rod specimen. If the standard deviation is calculated for the individual values obtained from each crack jump initiation point, the result is 5.0 percent on a total of 40 K_{IC} data points. The average standard deviation of the individual K_{IC} values obtained from a given short rod specimen was 4.3 percent for an average of four data points per specimen.

Since the standard deviations of individual K_{IC} measurements of Ref. 4 and of this study tend to be around 5 percent, it may be that this amount of scatter is a characteristic of the material. This fact, as well as the average value of K_{IC} , should be taken into account in any design considerations.

The average stress intensity factor for crack arrest in the beryllium short rod specimens was $9.41 \text{ MPa}\sqrt{\text{m}}$ with a standard deviation of 2.8 percent.

TABLE 1—Summary of beryllium fracture toughness data.

CT Spec. No.	K_{Ic} (MPa \sqrt{m}) (per E 399) ^a	Short Rod Spec. No.	K_{Ic} (MPa \sqrt{m}) (Short Rod)	For Crack Arrest: K_{Ia} (MPa \sqrt{m}) (Short Rod)
1	10.30	1-1	10.89	9.71
		1-2	10.25	9.07
2	11.20	2-1	10.94	9.46
		2-2	10.76	9.54
3	10.22	3-1	10.33	9.15
		3-2	10.64	9.63
4	9.96	4-1	10.76	9.53
		4-2	10.80	9.38
5	10.30	5-1	10.02	8.94
		5-2	10.90	9.66
Average	10.40		10.63	9.41
Stan.Dev. (%)	4.5		3.0	2.8

^aExcept for fatigue pre-cracking.

This value is almost 90 percent of K_{IC} for the material. This crack arrest toughness is not inconsistent with values reported in the literature,¹ which vary from 63 percent to 93 percent of crack initiation toughness. However, it was noted that the short rod values of K_{Ia} tended to be smaller when the crack length at arrest was small, and progressively increased with increasing crack length. To illustrate, the ten-specimen average K_{Ia} obtained from the first crack arrest point which fell within the accepted compliance range was $8.98 \text{ MPa}\sqrt{\text{m}}$, while the ten-specimen average from the last arrest point to fall within the range was $9.84 \text{ MPa}\sqrt{\text{m}}$. This effect may be related to the dynamics involved in crack arrest, and to the fact that the crack surface area generated per unit length of crack advance is small initially in the chevron-notched short rod specimen, but increases with the crack length. Thus, the distance the crack can "coast" while using up the kinetic energy stored in the specimen arms should be greater for small crack lengths than for larger ones. Because of the relatively stiff machine loading conditions, the additional "coasting" of the crack at small crack lengths would tend to yield a smaller load at the final arrest point, and therefore a decreased calculated value of K_{Ia} . No such dynamic effect influences the values measured for K_{IC} , of course.

The present test series serves as a check on the short rod calibration constant for flatjack loading, A_F . The value of A_F was originally based on the value of A , which is the short rod calibration constant for grip loading conditions. However, a preliminary experimental compliance calibration,⁸ plus other evidence, led to increasing the value of A_F by ten percent to its present value of 8.26. The agreement between the CT and short rod specimen results of this study indicates that the upward adjustment in A_F was approximately correct.

Material and time economies should be possible by using the short rod method. Because of the several toughness values yielded by each short rod test, fewer tests may be needed to obtain a good estimate of beryllium fracture toughness; a four-fold decrease in the number of tests may be possible. Also, the short rod specimen is much smaller than the CT specimen. Little time is required for each test: about two minutes to run the actual test, and about 20 minutes to do the data reduction using a programmable hand calculator. It is even possible to obtain fairly accurate toughness values by visually matching a smooth curve to the test data.

SUMMARY

Two fracture toughness test series were run on one batch of CIP/HIP-1 beryllium. The material was first machined into CT test specimens, tested, and then the tested halves were machined into short rods and tested. The agreement was very good between the results of the two test series. The toughness as indicated by the CT tests is $10.40 \text{ MPa}\sqrt{\text{m}}$ with an associated standard deviation of 4.5 percent. The toughness according to the short rod tests is $10.63 \text{ MPa}\sqrt{\text{m}}$ with a standard deviation of 3.0 percent. The values obtained in this study for the fracture toughness of beryllium compare favorably with previously published results for a similar beryllium pressing, where the average fracture toughness for the five best data sets was $10.37 \text{ MPa}\sqrt{\text{m}}$, and the average standard deviation was 5.5 percent. The better-than-average grouping of the short rod test results is due to the fact that each specimen toughness value represents the average of several individual toughness readings. Hence, there may be required fewer short rod tests than CT tests to obtain an adequate estimate of the fracture toughness of a particular beryllium pressing. Also, a measure of the crack arrest toughness is easily obtained from short rod tests. These facts, coupled with the ease of making and testing short rods, should make the short rod method a desirable way to test the fracture toughness of beryllium.

REFERENCES

1. Jones, M. H., Bubsey, R. T., and Brown, W. F. Jr., *Journal of Testing and Evaluation*, Vol. 1, No. 2, March 1973, pp. 100-109.
2. Conrad, H., Hurd, J., and Woodard, P., *Journal of Testing and Evaluation*, Vol. 1, No. 2, March 1973, pp. 88-99.
3. ASTM E 399-74, "Standard Method of Test for Plane-Strain Fracture Toughness of Metallic Materials."
4. Conrad, H., and Sargent, G. A., "Round Robin Test Program to Establish a Standard ASTM Method for Fracture Toughness of Beryllium," Final Report to NASA-Lewis, NASA Grant NSG-3013, March 1978.
5. Barker, L. M., *Engineering Fracture Mechanics*, Vol. 9, No. 2, 1977, pp. 361-369.
6. Barker, L. M., in *Fracture Mechanics of Ceramics*, Vol. 3, edited by R. C. Brandt, D. P. H. Hasselman, and F. F. Lange, Plenum, 1978, pp. 483-494.
7. Chou, S. C., Aronin, L. R., Dignam, J. F., and Rainey, J. H., "Mechanical Behavior of CIP/HIP-1 Beryllium as a Function of Strain Rate and Stress History," *Proceedings of the Fourth International Conference on Beryllium*, London, England, Oct. 4-7, 1977.
8. Barker, L. M., and Guest, R. V., "Compliance Calibration of the Short Rod Fracture Toughness Specimen," Terra Tek Report TR 78-20, 1978.

Any Material and Methods Research Center,
Natick, Massachusetts 01901
EVALUATION OF THE SHORT AND MEDIUM RANGE
EFFECTS OF THE FRACTURE TREATMENT OF BERYLLIUM
ON THE FRACTURE TREATMENT OF BERYLLIUM
SANDY V. GARDNER - Natick, Mass., U.S.A.

Final Report ARS 79-23, May 29, 1979, 25 pp.
1116 - Natick, Contract Number 79-C-233
SVA Project 62333302023. Natick Code:
623333-2333-02

The fracture toughness of CP-100-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 procedure, using a fatigue pre-crack of about 0.2 in. as opposed to the 0.5 in. required by E 399. This was done to avoid the difficulties of fatigue pre-cracking. The CT specimens were tested with a load range of 1000 to 2000 lbs. The average CT fracture toughness values were then calculated from the load range and the specimen geometry. The average CT fracture toughness was measured by the short rod method. The average of the short rod measurements of the fracture toughness was compared to the average of the CT measurements. In addition, the short rod tests provided a measure of the average of the CT measurements by about 3 percent. These results, together with the slippage of the short rod tests, indicate that a fatigue pre-crack is required, with the short rod method, to obtain a measure of the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Beryllium
Fracture toughness
Mechanical tests
Screens

Any Material and Methods Research Center,
Natick, Massachusetts 01901
EVALUATION OF THE SHORT AND MEDIUM RANGE
EFFECTS OF THE FRACTURE TREATMENT OF BERYLLIUM
ON THE FRACTURE TREATMENT OF BERYLLIUM
SANDY V. GARDNER - Natick, Mass., U.S.A.

Final Report ARS 79-23, May 29, 1979, 25 pp.
1116 - Natick, Contract Number 79-C-233
SVA Project 62333302023. Natick Code:
623333-2333-02

The fracture toughness of CP-100-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 procedure, using a fatigue pre-crack of about 0.2 in. as opposed to the 0.5 in. required by E 399. This was done to avoid the difficulties of fatigue pre-cracking. The CT specimens were tested with a load range of 1000 to 2000 lbs. The average CT fracture toughness values were then calculated from the load range and the specimen geometry. The average CT fracture toughness was measured by the short rod method. The average of the short rod measurements of the fracture toughness was compared to the average of the CT measurements. In addition, the short rod tests provided a measure of the average of the CT measurements by about 3 percent. These results, together with the slippage of the short rod tests, indicate that a fatigue pre-crack is required, with the short rod method, to obtain a measure of the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Beryllium
Fracture toughness
Mechanical tests
Screens

Any Material and Methods Research Center,
Natick, Massachusetts 01901
EVALUATION OF THE SHORT AND MEDIUM RANGE
EFFECTS OF THE FRACTURE TREATMENT OF BERYLLIUM
ON THE FRACTURE TREATMENT OF BERYLLIUM
SANDY V. GARDNER - Natick, Mass., U.S.A.

Final Report ARS 79-23, May 29, 1979, 25 pp.
1116 - Natick, Contract Number 79-C-233
SVA Project 62333302023. Natick Code:
623333-2333-02

The fracture toughness of CP-100-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 procedure, using a fatigue pre-crack of about 0.2 in. as opposed to the 0.5 in. required by E 399. This was done to avoid the difficulties of fatigue pre-cracking. The CT specimens were tested with a load range of 1000 to 2000 lbs. The average CT fracture toughness values were then calculated from the load range and the specimen geometry. The average CT fracture toughness was measured by the short rod method. The average of the short rod measurements of the fracture toughness was compared to the average of the CT measurements. In addition, the short rod tests provided a measure of the average of the CT measurements by about 3 percent. These results, together with the slippage of the short rod tests, indicate that a fatigue pre-crack is required, with the short rod method, to obtain a measure of the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Beryllium
Fracture toughness
Mechanical tests
Screens

Any Material and Methods Research Center,
Natick, Massachusetts 01901
EVALUATION OF THE SHORT AND MEDIUM RANGE
EFFECTS OF THE FRACTURE TREATMENT OF BERYLLIUM
ON THE FRACTURE TREATMENT OF BERYLLIUM
SANDY V. GARDNER - Natick, Mass., U.S.A.

Final Report ARS 79-23, May 29, 1979, 25 pp.
1116 - Natick, Contract Number 79-C-233
SVA Project 62333302023. Natick Code:
623333-2333-02

The fracture toughness of CP-100-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 procedure, using a fatigue pre-crack of about 0.2 in. as opposed to the 0.5 in. required by E 399. This was done to avoid the difficulties of fatigue pre-cracking. The CT specimens were tested with a load range of 1000 to 2000 lbs. The average CT fracture toughness values were then calculated from the load range and the specimen geometry. The average CT fracture toughness was measured by the short rod method. The average of the short rod measurements of the fracture toughness was compared to the average of the CT measurements. In addition, the short rod tests provided a measure of the average of the CT measurements by about 3 percent. These results, together with the slippage of the short rod tests, indicate that a fatigue pre-crack is required, with the short rod method, to obtain a measure of the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Key Words
Beryllium
Fracture toughness
Mechanical tests
Screens

Any Material and Mechanics Research Center,
Massachusetts 02172
EVALUATION OF THE SHORT AND MEDIUM PIV
MEASUREMENTS OF FRACTURE TOUGHNESS OF BERYLLIUM
Lynn H. Barber - Terra Val, Inc.
Donald V. Gault - Terra Val, Inc.

Final Report AEC-117-21, May 1979, 25 pp.
111m - Lab. No. Contract Number 79-C-003
DA Project BR3333333333. AEC-117-21
G33333.21336.03

The fracture toughness of CP/MIP-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 method except for the design pre-crack of about 0.5 mm, as opposed to the 0.5 mm required by E 399. The CT measurements were difficult to obtain pre-cracks. The CT measurements agreed very well with previous measurements of the fracture toughness of beryllium. The tested CT specimens had no visible surface defects and the fracture toughness was measured by the short rod method. The average CT measurement was 1.5 MPa√m. From the average CT measurement of about 1.5 MPa√m, the average CT measurement of about 1.5 MPa√m was determined. These results, together with the simplicity of the stress intensity factor method, allow a simple design pre-crack to be used. These results, together with the simplicity of the short rod test, allow a simple design pre-crack to be used, with the short rod method attractive for measuring the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Any Source
Beryllium
Fracture tests
Fracture strength
Mechanical tests
Stress

Any Material and Mechanics Research Center,
Massachusetts 02172
EVALUATION OF THE SHORT AND MEDIUM PIV
MEASUREMENTS OF FRACTURE TOUGHNESS OF BERYLLIUM
Lynn H. Barber - Terra Val, Inc.
Donald V. Gault - Terra Val, Inc.

Final Report AEC-117-21, May 1979, 25 pp.
111m - Lab. No. Contract Number 79-C-003
DA Project BR3333333333. AEC-117-21
G33333.21336.03

The fracture toughness of CP/MIP-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 method except for the design pre-crack of about 0.5 mm, as opposed to the 0.5 mm required by E 399. The CT measurements were difficult to obtain pre-cracks. The CT measurements agreed very well with previous measurements of the fracture toughness of beryllium. The tested CT specimens had no visible surface defects and the fracture toughness was measured by the short rod method. The average CT measurement was 1.5 MPa√m. From the average CT measurement of about 1.5 MPa√m, the average CT measurement of about 1.5 MPa√m was determined. These results, together with the simplicity of the stress intensity factor method, allow a simple design pre-crack to be used. These results, together with the simplicity of the short rod test, allow a simple design pre-crack to be used, with the short rod method attractive for measuring the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Any Source
Beryllium
Fracture tests
Fracture strength
Mechanical tests
Stress

Any Material and Mechanics Research Center,
Massachusetts 02172
EVALUATION OF THE SHORT AND MEDIUM PIV
MEASUREMENTS OF FRACTURE TOUGHNESS OF BERYLLIUM
Lynn H. Barber - Terra Val, Inc.
Donald V. Gault - Terra Val, Inc.

Final Report AEC-117-21, May 1979, 25 pp.
111m - Lab. No. Contract Number 79-C-003
DA Project BR3333333333. AEC-117-21
G33333.21336.03

The fracture toughness of CP/MIP-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 method except for the design pre-crack of about 0.5 mm, as opposed to the 0.5 mm required by E 399. The CT measurements were difficult to obtain pre-cracks. The CT measurements agreed very well with previous measurements of the fracture toughness of beryllium. The tested CT specimens had no visible surface defects and the fracture toughness was measured by the short rod method. The average CT measurement was 1.5 MPa√m. From the average CT measurement of about 1.5 MPa√m, the average CT measurement of about 1.5 MPa√m was determined. These results, together with the simplicity of the stress intensity factor method, allow a simple design pre-crack to be used. These results, together with the simplicity of the short rod test, allow a simple design pre-crack to be used, with the short rod method attractive for measuring the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Any Source
Beryllium
Fracture tests
Fracture strength
Mechanical tests
Stress

Any Material and Mechanics Research Center,
Massachusetts 02172
EVALUATION OF THE SHORT AND MEDIUM PIV
MEASUREMENTS OF FRACTURE TOUGHNESS OF BERYLLIUM
Lynn H. Barber - Terra Val, Inc.
Donald V. Gault - Terra Val, Inc.

Final Report AEC-117-21, May 1979, 25 pp.
111m - Lab. No. Contract Number 79-C-003
DA Project BR3333333333. AEC-117-21
G33333.21336.03

The fracture toughness of CP/MIP-1 beryllium was measured by testing five compact toughness (CT) specimens, following the ASTM E 399 method except for the design pre-crack of about 0.5 mm, as opposed to the 0.5 mm required by E 399. The CT measurements were difficult to obtain pre-cracks. The CT measurements agreed very well with previous measurements of the fracture toughness of beryllium. The tested CT specimens had no visible surface defects and the fracture toughness was measured by the short rod method. The average CT measurement was 1.5 MPa√m. From the average CT measurement of about 1.5 MPa√m, the average CT measurement of about 1.5 MPa√m was determined. These results, together with the simplicity of the stress intensity factor method, allow a simple design pre-crack to be used. These results, together with the simplicity of the short rod test, allow a simple design pre-crack to be used, with the short rod method attractive for measuring the fracture toughness of beryllium.

UNCLASSIFIED
UNLIMITED DISTRIBUTION

Any Source
Beryllium
Fracture tests
Fracture strength
Mechanical tests
Stress

DISTRIBUTION LIST

No. of Copies

Office of Deputy Under Secretary of Defense
for Research and Engineering (ET)
ATTN: Mr. J. Persh, Staff Specialist for Materials
and Structures (Room 3D1089) 1
The Pentagon
Washington, DC 20301

Office of Deputy Chief of Research Development
and Acquisition
ATTN: DAMA-CSS-D/Dr. J. I. Bryant (Room 3D424) 1
The Pentagon
Washington, DC 20310

Commander
U.S. Army Materiel Development and Readiness Command
ATTN: DRCLDC, Mr. R. J. Zentner 1
5001 Eisenhower Avenue
Alexandria, VA 22333

Director
Ballistic Missile Defense Systems Command
ATTN: BMDSC-TEN, Mr. N. J. Hurst 1
BMDSC-H 1
BMDSC-T 1
BMDSC-AOLIB 1
P. O. Box 1500
Huntsville, AL 35807

Ballistic Missile Defense Program Office
ATTN: DACS-BMT 1
DARCOM Bldg., Seventh Floor
5001 Eisenhower Avenue
Alexandria, VA 22333

Director
Ballistic Missile Defense Advanced Technology Center
ATTN: ATC-M, Mr. M. Whitfield 1
ATC-M, Dr. D. Harmon 1
ATC-M, Mr. J. Papadopoulos 1
P. O. Box 1500
Huntsville, AL 35807

No. of Copies

Director
Defense Nuclear Agency
ATTN: SPAS, Mr. J. F. Moulton, Jr. 1
 SPAS, Mr. D. Kohler 1
Washington, DC 20305

Director
Army Ballistic Research Laboratories
ATTN: DRDAR-BLT, Dr. N. J. Huffington, Jr. 1
 DRDAR-BLT, Dr. T. W. Wright 1
 DRDAR-BLT, Dr. G. L. Moss 1
Aberdeen Proving Ground, MD 21005

Commander
Harry Diamond Laboratories
ATTN: DRXDO-NP, Dr. F. Wimenitz 1
2800 Powder Mill Road
Adelphi, MD 20783

Commander
U.S. Army Combat Development Command
Institute of Nuclear Studies
ATTN: Technical Library 1
Fort Bliss, Texas 79916

Commander
Air Force Materials Laboratory
Air Force Systems Command
ATTN: LNE/Dr. W. Kessler 1
 LNC/Dr. D. Schmidt 1
Wright-Patterson Air Force Base, Ohio 45433

Space and Missile Systems Organization
ATTN: RSSE/LTC J. McCormack 2
P. O. Box 92960
World Way Postal Center
Los Angeles, CA 90009

Commander
Naval Ordnance Systems Command
ATTN: ORD-03331, Mr. M. Kinna 1
Washington, DC 20360

Commander
Naval Surface Weapons Center
ATTN: Dr. C. Lyons 1
 Dr. W. Messick 1
Silver Springs, MD 20910

No. of Copies

Naval Air Development Center ATTN: G. L. London (Code 3023) Warminster, PA 18974	1
Lawrence Livermore Laboratory ATTN: Lee Roberts James E. Hanafee P. O. Box 808 Livermore, CA 94550	1 1
Los Alamos Scientific Laboratory ATTN: GMX-6, Dr. J. W. Taylor Jack E. Hockett P. O. Box 1663 Los Alamos, NM 87544	1 1
Sandia Laboratories ATTN: Dr. W. Herrmann Dr. L. D. Bertholf Dr. J. Lipkin P. O. Box 5800 Albuquerque, NM 87115	1 1 1
Sandia Laboratories ATTN: Donald R. Adolphson J. E. Smugeresky B. C. Odegard Livermore, CA 94550	1 1 1
Aerospace Corporation ATTN: Dr. R. Cooper Dr. W. Barry P. O. Box 92957 Los Angeles, CA 90009	1 1
AVCO Corporation Government Products Group ATTN: Dr. W. Reinecke Mr. P. Rolincik 201 Lowell Street Wilmington, MA 01997	1 1
Battelle Memorial Institute ATTN: John Mueller 505 King Avenue Columbus, OH 43201	1

No. of Copies

Brush Wellman Corporation
ATTN: James Stonehouse 1
17676 St. Clair Avenue
Cleveland, Ohio 44114

ETA Corporation
ATTN: Mr. D. L. Mykkanen 1
P. O. Box 6625
Orange, CA 92667

Effects Technology, Inc.
ATTN: Dr. R. Wengler 1
Dr. R. Parisse 1
Mr. J. Green 1
5383 Hollister Avenue
Santa Barbara, CA 93111

Fiber Materials, Inc.
ATTN: Mr. M. Subilia, Jr. 1
Mr. L. Landers 1
Mr. G. Williams 1
Mr. P. Marchol 1
Biddeford Industrial Park
Biddeford, ME 04005

S. H. Gelles Associates
ATTN: S. H. Gelles 1
2840 Fisher Road
Columbus, OH 43204

General Electric Company
Valley Forge Space Technology Center
ATTN: K. Hall 1
J. Brazel 1
Ms. B. McGuire 1
P. O. Box 8555
Philadelphia, PA 19101

General Dynamics Corporation
Convair Division
ATTN: J. Hertz 1
H. McCutcheon, Jr. 1
5001 Kearny Villa Road
San Diego, CA 92138

Kaman Sciences Corporation
ATTN: F. Shelton 1
P. O. Box 7463
Colorado Springs, CO 80933

Kawecki Berylco Industries, Inc.
ATTN: Norman P. Pinto 1
P. O. BOX 1462
Reading, PA 19603

No. of Copies

Ktech ATTN: Dr. D. Keller 911 Pennsylvania Avenue, N.E. Albuquerque, NM 87110	1
Lockheed Palo Alto Research Laboratory ATTN: Donald Webster 3251 Hanover Street Palo Alto, CA 94304	1
Lockheed Missiles and Space Company ATTN: D. Aspinwall Matthew V. Rebholz P. O. Box 504 Sunnyvale, CA 94088	1 1
Martin Marietta Corporation ATTN: Dr. M. Hendricks R. Hewitt Frank H. Koo P. O. Box 5837 Orlando, FL 32805	1 1 1
McDonnell Douglas Corporation ATTN: Dr. L. Cohen H. Parachanian 5301 Bolsa Avenue Huntington Beach, CA 92647	1 1
Prototype Development Associates, Inc. ATTN: J. Schultzler N. Harrington 1740 Garry Avenue, Suite 201 Santa Ana, CA 92705	1 1
R&D Associates ATTN: Dr. A. Field 525 Wilshire Blvd. Santa Monica, CA 90025	1
Radkowski Associates ATTN: Dr. P. Radkowski P. O. Box 5474 Riverside, CA 92507	1
Rockwell International Rocky Flats Plant ATTN: S. Beitscher P. O. Box 464 Golden, CO 80401	1

No. of Copies

Southwest Research Institute
ATTN: Mr. A. Wenzel 1
8500 Culebra Road
San Antonio, TX 78206

Stanford Research Institute
ATTN: Dr. D. Curran 1
Dr. L. Seaman 1
333 Ravenswood Avenue
Menlo Park, CA 90250

TRW Systems Group
ATTN: D. Gamble 1
One Space Park
Redondo, Beach, CA 90278

Lehigh University
Institute of Fracture and Solid Mechanics
ATTN: Dr. George C. Sih 1
Packard Lab., Bldg. #19
Bethlehem, PA 18015

Stanford University
Department of Applied Mechanics
ATTN: Professor E. H. Lee 1
Stanford, CA 94305

Defense Documentation Center 1
Cameron Station, Bldg. 5
5010 Duke Station
Alexandria, VA 22314

Director
Army Materials & Mechanics Research Center
ATTN: DRXMR-H, J. F. Dignam 1
DRXMR-H, L. R. Aronin 1
DRXMR-H, Dr. S. C. Chou 1
DRXMR-H, Dr. D. P. Dandekar 1
DRXMR-AP 1
DRXMR-PL 2
DRXMR-PR 1
Watertown, MA 02172