

AD-A137 519

SIZE DISTRIBUTION FOR G P ZONES IN DILUTE AL-ZN ALLOYS
(U) NORTHWESTERN UNIV EVANSTON IL DEPT OF MATERIALS
SCIENCE R G PAHL ET AL. 09 JAN 84 TR-12

1/1


UNCLASSIFIED

N00014-80-C-0116

F/G 11/6

NL



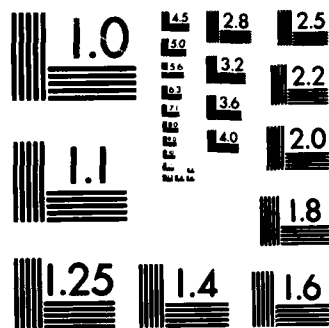

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD A137519

NORTHWESTERN UNIVERSITY

DEPARTMENT OF MATERIALS SCIENCE

Technical Report No. 12
January 9, 1984

Office of Naval Research
Contract N00014-80-C-0116

SIZE DISTRIBUTION FOR G. P. ZONES IN DILUTE AL-ZN ALLOYS

BY

R. G. Pahl, Jr. and J. B. Cohen


Distribution of this document
is unlimited.

Reproduction in whole or in
part is permitted for any
purpose of the United States
Government.



DTIC FILE COPY

EVANSTON, ILLINOIS

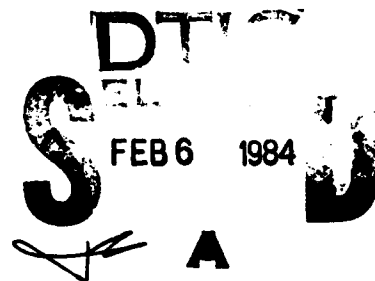

84 02 6 112

THE SIZE DISTRIBUTION FOR G. P. ZONES IN DILUTE AL-ZN ALLOYS

R. G. Pahl, Jr. and J. B. Cohen

Department of Materials Science and Engineering
The Technological Institute, Northwestern University
Evanston, IL 60201 USA

Introduction

There is considerable current interest in the theory of particle coarsening. The original theories by Lifshitz and Slyozov (1) and Wagner (2) assume no particle interactions and therefore apply strictly only to the limiting case of zero volume fraction of second phase. Marqusee and Ross (3) have recently provided a very clear treatment of this problem. Sauthoff and Kahlweit (4) have taken into account variation of the diffusion coefficient with coherency, Ardell (5) introduced a modification which takes into account particle interactions, and the various possibilities for the diffusion geometry have been extended by Tsumuraya and Mayata (6). Particle encounters have been treated by Davies et al (7), and Brailsford and Wynblatt (8) have developed a theory that assumes that the growth of any particle is a function of the entire size distribution. The primary motivation for all these treatments is the fact that the experimentally determined particle size distributions do not agree with the LSW theory; in particular, they are broader than predicted, and do not exhibit the sharp cut-off at some maximum size. This topic is nicely reviewed in ref. 6, where much of the available data is considered (but see also refs. 9-11). The authors conclude that "the application of the models to experiment must await the acquisition of size distribution histograms in a variety of systems with reduced statistical errors." Glicksman and Voorhees (12) have just completed a new theoretical study via computer simulation, showing that the shape of the size distribution varies considerably with volume fraction of the second phase. At 0.5 or more, the asymmetry to small sizes characteristic of the LSW theory and its various modifications vanishes, and is replaced by an asymmetry to large sizes. A similar result has been obtained by Marqusee and Ross (13).

The Al-Zn system is particularly attractive for a comparison between theory and experiment because the G. P. zones that form during aging are coherent (with modest coherency strains), equiaxed, and randomly distributed. The volume fraction can be varied appreciably, and with small-angle scattering it is possible to obtain the entire size distribution from a large number of zones ($\sim 10^{18}$). Here we present such a study carried out with x-rays after various aging treatments, and after aging and fatigue to stimulate zone growth.

Experimental Procedures

The samples were made from alloy rods 3.5 and 5.3 at pct. Zn (which will form 2 and 4 volume percent zones (14)). Rolled and annealed strip, 0.8 mm thick, was given a strain of 1-2 pct. and lowered slowly into a salt bath at 803°K, to produce coarse grains 1-3 mm in size. A solution heat treatment at 698°K for 14 hrs. was followed by an air cool, reversion at 523°K, and re-aging at various temperatures, from room temperature to 373°K. (A few samples were subjected to ~ 10 cycles at 3.3 ksi before reversion, to reduce the tendency for grain boundary cracking (15).) Some specimens were also fatigued to stimulate zone growth. An Instron electrohydraulic machine was employed for this purpose, in pull-pull under strain control, or in push-pull (R=-1) with dynamic displacement control. Strains were measured with a clip-on extensometer, and both high- and low-cycle regimes were employed.

X-ray small-angle scattering was obtained with a Rigaku 12 kw generator operated in point focus with filtered MoK radiation, and a circular slit system (0.5 and 0.3 mm slits 250 mm apart to define the x-ray beam). In this way, the beam was considerably smaller than the grain size, and also no slit collimation corrections were required. The peak from a thin polystyrene sheet placed in the beam was employed to normalize different runs, and as well, to detect any changes

in the intensity of the incident x-ray beam during a set of experiments. Parasitic scattering was measured without the sample, and corrected for sample absorption prior to subtraction. Total counts accumulated ranged from 3000 to 10000 (taking 10 hrs. to 2 days per measurement), and the parasitic intensity was 15 pct. or less. A linear position sensitive proportional detector was used; its linearity and uniformity were carefully examined. Large tilts of a sample around the incident beam were made to see if the zones were truly spherical, since it is known that as the zones grow in this system, they can become ellipsoidal (16). No such case is included in the data presented here. Particle size distribution were obtained following Letcher and Schmidt (17) and Brill and Schmidt (18). As a check on the distributions, the moments that correspond to the Guinier and Porod radii were calculated, and compared to the values obtained directly from the data. Porod plots (for the most part) exhibited horizontal segments, indicating sharp interfaces at the zone boundaries. In many of the samples, the integrated intensity was the same before and after fatigue, indicating that coarsening was occurring. But some samples were studied in which the volume fraction increased during fatigue.

Fifteen different samples were examined and Table I summarizes the various treatments, integrated intensities, and average zone sizes. Further details can be found in ref. 19, and will be published in a paper concerned with the specific effects of fatigue on G. P. zones.

Results and Discussion

All of the size distributions superimpose, as shown in Fig. 1. This indicates that the measurements were made in the coarsening stage. [The superposition also implies that scaling holds]

It is abundantly clear from Fig. 1 that despite the small volume fraction of zones, the size distribution is broader than that predicted by LSW theory, or any of its modifications. Also, the distribution is asymmetric toward large sizes, whereas theory predicts asymmetry to small sizes. None of the available theoretical treatments of coarsening can explain these results. The curve is also broader than a log-normal distribution. These alloys decompose inside the spinodal, and it appears that the diffusion paths are affected. Cahn (20) showed that a spinodally decomposed alloy would resist coarsening, and Weins and Cahn (21) found that if the particles surrounding any given particle were quite similar, the coarsening rate was reduced. While these treatments provide a qualitative explanation for our results, a more complete quantitative theory of coarsening is needed, to take into account the role of the initial distribution on the asymptotic solution. Topology and percolation may be important factors in controlling the diffusion paths. Many of the current theories assume the particles are points.

[The results in Table I also show that fatigue accelerates zone growth. We consider these results in more detail in the paper mentioned above.]

Acknowledgements

This research was supported by ONR under contract number N00014-C-0116. The x-ray measurements were performed in the x-ray diffraction facility of Northwestern University's Materials Research Center, supported in part by the MRL program of NSF, grant number DMR-82-16972. Cycling was carried out in the mechanical behavior facilities of this center. We acknowledge suggestions on the data analysis by Dr. M. Yang, and on fatigue testing by Prof. T. Gross. Helpful discussions with Dr. J. Cahn and Prof. M. Glicksman are acknowledged.

References

1. I. M. Lifshitz and V. V. Slyozov, *J. Phys. Chem. Solids* 19, 315 (1961).
2. C. Wagner, *Z. Electrochem.* 65, 581 (1961).
3. J. A. Marqusee and J. Ross, *J. Chem. Phys.* 79, 373 (1983).
4. G. Sauthoff and M. Kahlweit, *Acta metall.* 17, 1501 (1969).
5. A. J. Ardell, *Acta metall.* 20, 61 (1972).
6. K. Tsunuraya and Y. Miyata, *Acta metall.* 31, 437 (1983).
7. C. K. L. Davies, P. Nash and R. N. Stevens, *Acta metall.* 28, 179 (1980).
8. A. D. Brailsford and P. Wynblatt, *Acta metall.* 27, 489 (1979).
9. G. P. Wirtz and M. E. Fine, *J. Amer. Ceramic Soc.* 51, 402 (1968).
10. G. Cocco, L. Schiffrini, S. Enzo and A. Benedetti, *Phys. Stat. Sol. (a)* 69, 343 (1982).
11. H. Calderone and M. E. Fine, to be published.
12. M. E. Glicksman and P. W. Voorhees, *Intl. Conf. on Phase Transf., Crete, 1983*, in press.
13. J. A. Marqusee and J. Ross, private communication.
14. K. G. Satyanara, *J. Mat. Sci.* 16, 1233 (1981).
15. M. C. Lu and S. Weissmann, *Mat. Sci. Eng.* 32, 41 (1977)

16. M. Morinaga, K. S. Liu, Y. Tomita and Y. Murakami, Trans. JIM 15, 1 (1974).
17. J. H. Letcher and P. W. Schmidt, J. Appl. Phys. 37, 649 (1966).
18. O. L. Brill and P. W. Schmidt, J. Appl. Phys. 39, 2274 (1968).
19. R. Pahl, Ph.D. thesis, Northwestern Univ., August, 1983
20. J. W. Cahn, Acta metall. 14, 1685 (1966).
21. J. J. Weins and J. W. Cahn, Sintering and Related Phenomena (ed. G. C. Kuczynski), p. 151, Plenum Press, New York (1973).

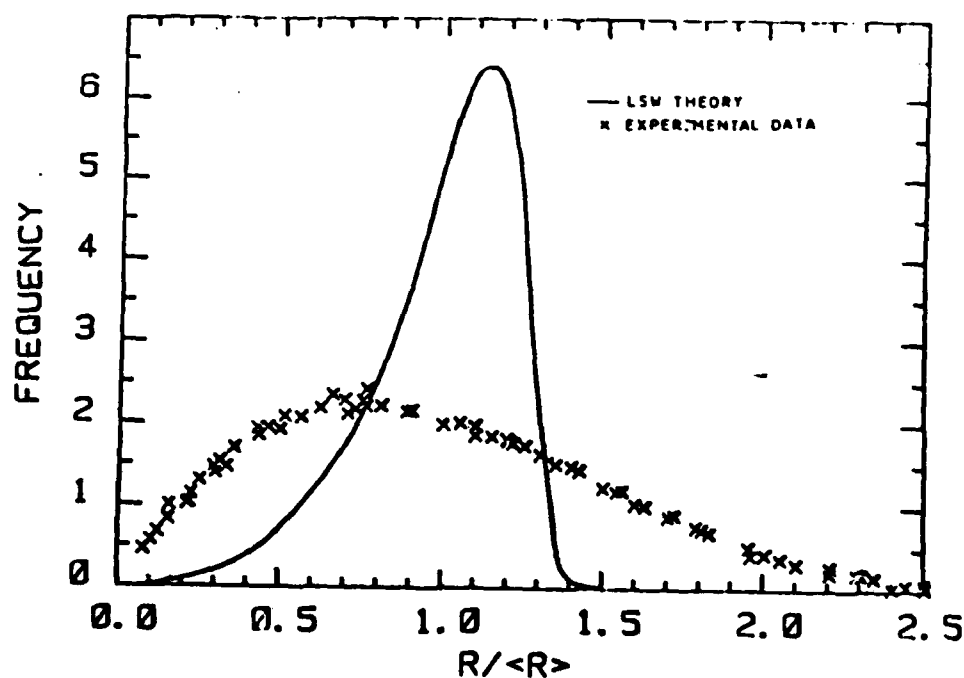


FIG. 1

Size distribution comparison, theoretical and experimental (x). (The x's include all 15 samples.)

Accession For

NTIS GRA&I

or TAB

Unannounced

Notification

On

Distribution/

Availability Codes

Available for

Use in the



A1

TABLE I
Results of SAXS

SAMPLE (a/oZn)	HEAT TREATMENT ^x	FATIGUE $\Sigma \Delta \sigma_p$ (%)	R_{GLS}^o (Å)	R_{GSD} (Å)	R_{PLS} (Å)	R_{PSD} (Å)	FLAT POROD REGION	<D>	Q(Z RELATIVE TO FULLY AGED)
P(3.5a/oZn)	1	—	14.6	15.0	10.9	13.8	Yes	18.4	100
	2	.50	6.0	6.5	5.3	6.3		9.1	64
	2	7.0	9.0	8.6	6.3	8.3		11.2	100
	2	43.5	13.8	13.1	6.7	12.6		17.2	100
L(3.5a/oZn)	#3 100 cycles ##3grainA @ ± 14.5 ksi 3grainB @ 77°K		6.5	6.4	4.5	6.1		8.2	*
			8.6	8.5	6.6	8.2		11.1	65
			9.8	10.0	6.0	9.7		13.2	100
S(5.3a/oZn)	1	—	19.3	20.3	15.4	17.5	Yes	22.5	100
	4	1.85	15.2	15.2	13.6	14.5		19.5	20
	4	8.60	17.6	18.0	13.7	16.7	Yes	22.7	61
	4	9.10	13.6	13.6	9.7	12.9	No	17.5	98
V(5.3a/oZn)	5	—	13.5	13.4	10.3	12.9	No	17.5	100
	5grainA	3.50	19.9	18.9	14.0	17.8	No	23.9	93
	5grainB	3.50	22.5	22.3	17.7	19.5	No	25.4	87
T(5.3a/oZn)	5	—	21.3	21.0	17.9	18.2	Yes	23.7	100

[†]Aging occurs during 12 hr. SAXS measurement at 178°K.

^{##}Additional aging occurs during 1-2 days of further SAXS measurements at 298°K.

OLS is result of least square fit to Guinier or Porod approximation.

SD is result from the ratio of moments of the size distribution.

^{*}The low temperature GP zone composition is not sufficiently well defined to estimate state of completion of aging.

- ^x1. Homogenize at 698°K/14hr.; air cool; solutionize at 698°K/1 hr.; water quench to 298°K; age at 298°K/2 days.
2. Treatment #1 above plus: 2×10^4 cycles @ ± 3.3 ksi; reversion at 423°K/20mins.; re-age at 351°K/64hrs.
3. Treatment #1 above plus: reversion at 423°K/20mins.; re-age at 298°K/14 days.
4. Treatment #1 above plus: 2×10^4 cycles @ ± 3.3 ksi; reversion at 423°K/20mins.; re-age at 373°K/18hrs.
5. Homogenize at 698°K/14hrs.; air cool; reversion at 523°K/30mins.; re-age at 298°K ~ 6 months.

DOCUMENT CONTROL DATA - R & D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author) J. B. Cohen Northwestern University Evanston, Illinois 60201		2a. REPORT SECURITY CLASSIFICATION Unclassified	
		2b. GROUP	
3. REPORT TITLE SIZE DISTRIBUTION FOR G. P. ZONES IN DILUTE AL-ZN ALLOYS			
4. DESCRIPTIVE NOTES (Type of report and inclusive dates) Technical Report No. 12			
5. AUTHOR(S) (First name, middle initial, last name) R. G. Pahl, Jr. and J. B. Cohen			
6. REPORT DATE January 9, 1984		7a. TOTAL NO. OF PAGES 7	7b. NO. OF REFS 21
8a. CONTRACT OR GRANT NO. N00014-80-C-0116		9a. ORIGINATOR'S REPORT NUMBER(S) 12	
b. PROJECT NO. Mod. No. P00002		9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)	
c.			
d.			
10. DISTRIBUTION STATEMENT Distribution of this document is unlimited			
11. SUPPLEMENTARY NOTES		12. SPONSORING MILITARY ACTIVITY Metallurgy Branch Office of Naval Research	
13. ABSTRACT The G.P. zone size distribution has been measured in dilute Al-Zn alloys via small-angle x-ray scattering. This distribution does not agree with current theories for the Ostwald ripening process.			

Unclassified

Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
G.P. zones, Al alloys, age hardening, size distribution, coarsening, Ostwald ripening.						

END

FILMED

3-84

DTIC