

December 1983

MCIC-HB-01R
Volume 3




AD-A141 901

Damage Tolerant Design Handbook

A Compilation of Fracture and Crack-Growth Data
for High Strength Alloys

DTIC FILE COPY

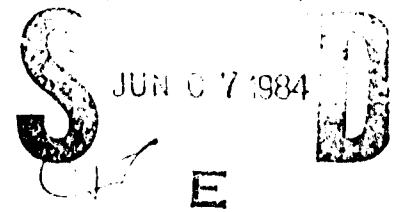

Metals and Ceramics Information Center
Battelle
Columbus Laboratories

Prepared by

University of Dayton Research Institute

Materials Laboratory
Air Force Wright Aeronautical Laboratories
Wright-Patterson Air Force Base

This report is available for public release and its distribution is unlimited.

81-07-10-11

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER MCIC-HB-01R (4 Volumes)	2. GOVT ACCESSION NO. DA 141901	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) DAMAGE TOLERANT DESIGN HANDBOOK. A COMPILATION OF FRACTURE AND CRACK GROWTH DATA FOR HIGH-STRENGTH ALLOYS	5. TYPE OF REPORT & PERIOD COVERED	
	6. PERFORMING ORG. REPORT NUMBER	
7. AUTHOR(s) J. Gallagher	8. CONTRACT OR GRANT NUMBER(s) F33615-80-C-5149 DLA900-83-C-1744	
9. PERFORMING ORGANIZATION NAME AND ADDRESS University of Dayton Research Institute 300 College Park Avenue Dayton, OH 45469	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS	
11. CONTROLLING OFFICE NAME AND ADDRESS Materials Laboratory (AFWAL/MLSE) Air Force Wright Aeronautical Laboratories (AFSC) Wright-Patterson AFB, OH 45433	12. REPORT DATE December 1983	
	13. NUMBER OF PAGES 3260	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) Unclassified	
15a. DECLASSIFICATION/DOWNGRADING SCHEDULE		
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release; Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Availability: Metals and Ceramics Information Center, P.O. Box 8128, Columbus, Ohio 43201 HC \$400.00 for 4 Volumes (No copies furnished by DTIC)		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) *Fracture (Mechanics), *Handbooks, *Titanium Alloys, *Nickel Alloys, *Stainless Steel, *Aluminum Alloys, High Strength Alloys, Structural Steel, Fracture Toughness, Damage Assessment, State of the Art, Data Compilation, Fatigue Crack Growth		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) This edition entirely revamps the 1975 edition. This edition is arranged by alloy rather than by property as in the previous addition. The data are presented in eight chapters and four volumes. Plane-strain fracture toughness (K_{IC}), critical plane stress fracture toughness, apparent fracture toughness, R-curve, fatigue crack growth rates, sustained-load crack growth rate and threshold stress intensity (K_{ISCC}) data are presented for stainless steels, titanium alloys, nickel-base alloys, alloy steels, 2000-, 6000- and 7000-series aluminum alloys.		

**DTIC
SELECTED
JUN 07 1984
E**

Damage Tolerant Design Handbook

A Compilation of Fracture and Crack Growth
Data for High-Strength Alloys

Compiled by
J. Gallagher
Program Manager
University of Dayton Research Institute
Dayton, Ohio

Sponsored by

Materials Laboratory
Air Force Wright Aeronautical Laboratories
Wright-Patterson Air Force Base, Ohio 45433

December 1983



Metals and Ceramics Information Center
BATTELLE
Columbus Laboratories
505 King Avenue
Columbus, Ohio 43201

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	<i>SET # 400</i>
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
<i>A-121</i>	

ACKNOWLEDGMENT

This document was published by the Metals and Ceramics Information Center (MCIC), Battelle's Columbus Laboratories, 505 King Avenue, Columbus, Ohio 43201-2693. MCIC's objective is to provide a comprehensive current resource of technical information on the development and utilization of advanced metal- or ceramic-base metals.

MCIC is publishing this revised and expanded edition of the Damage Tolerant Design Handbook to increase the availability of information to the technical community. The loose leaf format was selected to facilitate updating the handbook as new information becomes available. This edition is a completely revised and expanded version of the original handbook first published by MCIC in 1972 and revised in 1973 and 1975.

The Center is operated by Battelle-Columbus under Contract Number DLA900-83-C-1744 for the U.S. Defense Logistics Agency; technical aspects of MCIC operations are monitored by the Office of the Deputy Under Secretary of Defense Research and Advanced Technology. The support of these sponsor organizations is gratefully acknowledged.

This document was prepared under the sponsorship of the Department of Defense. Neither the United States Government nor any person acting on behalf of the United States Government assumes any liability resulting from the use or publication of the information contained in this document or warrants that such use or publication will be free from privately owned rights.

Approved for public release; distribution unlimited.

All rights reserved. This document, or parts thereof, may not be reproduced in any form without written permission of the Metals and Ceramics Information Center.

TABLE 1.4
 ABBREVIATIONS FOR MATERIAL SYSTEMS

<u>Abbreviation</u>	<u>Materials</u>
ALUM	Aluminum Alloys
TITAN.	Titanium Alloys
NICKEL	Nickel-Base Alloys
STAIN. STEEL	Stainless Steel Alloys
ALLOY STEEL	Steel Alloys

TABLE 1.5
 ABBREVIATIONS FOR ALLOY CONDITIONING AND HEAT TREATMENTS

<u>Abbreviation</u>	<u>Condition/Heat Treatment</u>
OQ	Oil Quenched
ABQ	Aus-Bay Quench
AC	Air Cool
WC	Water Quench
MA	Mill Anneal
BA	Beta Anneal
DA	Duplex Anneal
RA	Recrystallize Anneal
ST	Solution Treated
STA	Solution Treated and Aged

TABLE 1.6
 ABBREVIATIONS FOR PRODUCT FORMS

<u>Abbreviations</u>	<u>Product Form</u>
S	Sheet
P	Plate
E	Extrusion
F	Forging
FB	Forged Bar
BT	Billet
BR	Round Bar
RB	Rolled Bar
C	Casting
W	Weldment
D	Disk
EB	Extruded Bar
B	Bar

TABLE 1.7
ABBREVIATIONS FOR ENVIRONMENTAL SYSTEMS

<u>Abbreviations</u>	<u>Environmental System</u>
R. T.	Room Temperature (65°F-80°F)
L. H. A.	Low Humidity Air (< 10% RH)
Dry Air	Low Humidity Air (< 10% RH)
H. H. A.	High Humidity Air (> 80% RH)
Lab. Air	Laboratory Air (% RH unspecified)
Dist. H ₂ O	Distilled Water
Dist. Water	Distilled Water
3.5 PCT Nacl	3.5% Salt Water Solution
JP.4	JP-4 Aircraft Fuel
JP.4 - Fuel	JP-4 Aircraft Fuel
S. T. W.	Sump Tank Water
S. S. W.	Simulated Sea Water
S. C. S.	Shop Cleaning Solvent
F. C. S.	Field Cleaning Solvent
Salt Fog	Salt Fog
Temp.	Temperature

TABLE 1.8
ABBREVIATIONS FOR SPECIMEN DESIGNS

<u>Abbreviations</u>	<u>Specimen Design*</u>
CT	Compact Tension
NB	3Pt. Notched Bend
WOL	Wedge Open Load
CCP	Center Cracked Panel
BWOL	Bolt Loaded-Wedge Open Load
CANT	Cantilever Beam
TDCB	Tapered Double Cantilever Beam
CHAR	Charpy
PTSC	Part Through Surface Crack
SENT	Single Edge Notch Tension
K _B BAR	K _B Bar
4-NB	4 Pt. Notched Bend
MCT	Modified Compact Tension
CNT	Center Notched Tension
DCB	Double Cantilever Beam
BDCB	Bolt Loaded Double Cantilever Beam

*Also note that when "SG" is used in conjunction with a specimen design, the specimen is side-grooved along the path of the crack.

Volume 3

CONTENTS

CHAPTER 7 2000 AND 6000 SERIES ALUMINUM ALLOYS

2014	2024 (Alclad)	2324
2020	2048	2419
2020 (Alclad)	2124	2618
2021	2214	6061
2024	2219	

CHAPTER 8 7000 SERIES ALUMINUM ALLOYS

7001	7039	
7005	7049	
7007	7050	
7010	7050 (Alclad)	

CHAPTER 7

ALUMINUM 2000 AND 6000 SERIES ALLOY SECTIONS

7.0	2000 and 6000 Series Aluminum Material Summaries
7.1	2014
7.2	2020
7.3	2020 (Alclad)
7.4	2021
7.5	2024
7.6	2024 (Alclad)
7.7	2048
7.8	2124
7.9	2214
7.10	2219
7.11	2324
7.12	2419
7.13	2618
7.14	6061
7.15	Bibliography

TABLE 7.0.1
 AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	KIC	KC	R	CURVES	DA/DN	DA/DT	KIBCC
2014	T451	PLATE						X	
	T6	FORGING	X				X		X
		FORGED BAR	X				X		
		SHEET		X			X		
T61	ROLLED BAR		X			X			
	FORGING		X						
	FORGING		X						
	PLATE		X			X		X	
T652	FORGING		X						
	FORGING		X						
2020	T6	PLATE		X					
		EXTRUSION SHEET		X			X		
	T651	PLATE		X			X		X
		SHEET		X			X		X
2020 (ALCLAD)	T6	SHEET					X		
	T61	PLATE		X					X
PLATE			X						X
2021	T61 OVERHEATED WELD	PLATE		X					X
		PLATE		X					X
	T61 REPAIR WELD + AGE WITH 2319 FILLER WIRE	PLATE		X					X
		PLATE		X					X
T61 REPAIRED WELD AGED 16HR 325F WELD FUSION LINE	PLATE		X					X	
	PLATE		X					X	
T61 REPAIRED WELD AGED 16HR 325F WELD CENTER LINE	PLATE		X					X	
	PLATE		X					X	
T61 REPAIRED WELD AGED 16HR 325F HEAT AFFECTED ZONE	PLATE		X					X	
	PLATE		X					X	
T61 WELD + AGE WITH 2319 FILLER WIRE	PLATE		X					X	
	PLATE		X					X	

TABLE 7.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	KIC	KC	R	CURVES	DA/DN	DA/DT	KIBCC
2021	T81 WELDED AGED 16HR 325F HEAT AFFECTED ZONE	PLATE							X
	T81 WELDED AGED 16HR 325F WELD CENTER LINE	PLATE							X
	T81 WELDED AGED 16HR 325F FUSION LINE	PLATE							X
2024	T8151	PLATE	X						
	T3	SHEET PLATE		X X			X X		
	T351	PLATE EXTRUSION FORGED BAR SHEET	X X X		X		X	X	X
	T3511	EXTRUSION	X				X		
	T352	FORGING							X
	T36	SHEET		X					
	T4	SHEET FORGING		X				X	
	T42	PLATE					X		
	T6	SHEET		X					
	T62	SHEET						X	
	T62 (90)	SHEET PLATE		X				X	
	T62 (140)	SHEET PLATE		X				X	
	T81	SHEET PLATE		X				X	
	T851	PLATE SHEET		X X				X X	X
	T8510	EXTRUSION		X					

TABLE 7.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	MIC	KC	R	CURVES	DA/DN	DA/DT	KISCC
2024	T8511	EXTRUSION	X						
	T852	FORGING	X			X			X
	T86	SHEET		X					
	T861	SHEET PLATE				X X			
2024 (ALCLAD)	T3	SHEET		X			X		
	T86	SHEET		X					
2048	T851	PLATE	X			X			
2124	T351 (417)	PLATE	X						
		PLATE	X			X			X
	T851 (8P)	PLATE	X						
	T851 (417)	PLATE	X						
2214	T651	PLATE	X						
	T651 (417)	PLATE	X						
2319	T37	PLATE					X		X
	T81	SHEET				X			
	T851	PLATE FORGING SHEET	X X X						X

TABLE 7.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	R	CURVES	DA/DN	DA/DT	K1S2C
2219	T8511	EXTRUDED BAR					X		
		FORGING BILLET	X				X	X	
		PLATE SHEET	X	X	X				X
		PLATE	X						
2324	T39	PLATE					X		
		2419	T851	PLATE	X			X	
		2618	T61 T651 T81	SHEET					
PLATE	X								
SHEET							X		
6061	T6			SHEET				X	
6061	T651	PLATE FORGED BAR	X	X			X		X
		FORGING	X						X
		2652	T652	FORGING	X				

TABLE 7.0.2

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K _{IC} (KSI SQRT(IN))									
				L-T		S-L							
				SPECIMEN THICK #	MEAN STD. DEV.	SPECIMEN THICK #	MEAN STD. DEV.						
2014	T6	FORGING	0.89-8.00	0.71	27.9	0.8	0.25	17.4	1.7	0.75	16.9	1.9	
		FORGED BAR	4.50	---	---	0.25	16.7	0.6	---	---	---	---	
	T611	FORGING	1.00	---	---	---	---	---	---	---	0.75	17.8	0.6
		PLATE	1.00-5.00	1.00	23.3	1.0	1.00	21.4	1.2	0.50	17.8	0.1	
		FORGING	2.00-6.00	0.75	28.8	3.6	0.75	21.9	3.2	0.50	18.1	1.4	
2020	T651	PLATE	1.37	1.00	23.0	2.4	1.00	17.2	0.3	---	---	---	
2021	T81	PLATE	1.00	0.99	27.0	0.5	---	---	---	---	---	---	
		PLATE	1.00	---	---	---	1.00	15.8	0.7	---	---	---	
		PLATE	1.00	---	---	---	1.00	19.4	2.7	---	---	---	
2024	T351	PLATE	2.00-3.00	1.00	35.0	7.1	---	---	---	---	---	---	
		EXTRUSION	3.00-5.00	---	---	---	1.50	25.0	0.9	---	---	---	
	T3511	EXTRUSION	---	1.20	38.0	2.6	---	---	---	---	---	---	
		PLATE	0.37-4.00	0.38	23.3	2.4	0.38	20.7	1.9	---	---	---	
		EXTRUSION	2.76-4.50	1.86	30.4	2.7	2.00	16.5	1.0	1.00	15.7	1.4	
T8511	EXTRUSION	3.50	1.00	24.1	0.4	1.00	16.0	0.0	---	---	---		
	FORGING	2.00-6.00	0.75	29.2	5.2	0.75	18.9	2.6	0.25	15.9	0.8		
2048	T851	PLATE	1.00-4.00	1.00	37.9	1.9	1.00	30.6	2.5	0.75	25.4	1.9	

* MINIMUM SPECIMEN THICKNESS (IN)

TABLE 7.0.2 (con't)

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K1C (KSI SQRT(IN))								
				T-L		S-L						
				SPECIMEN THICK *	MEAN DEV	STD. DEV	SPECIMEN THICK *	MEAN DEV	STD. DEV			
2124	T851	PLATE	0.62-6.00	0.50	29.7	2.8	0.50	25.1	2.3	0.50	21.7	2.1
	T851 (SP)	PLATE	2.00-6.00	0.75	27.2	4.7	0.75	23.1	2.7	0.75	21.4	3.2
	T851 (417)	PLATE	1.57-5.50	0.50	28.9	2.8	0.50	23.8	2.4	0.50	21.3	2.0
2214	T651	PLATE	1.50-2.37	1.00	35.3	2.7	1.00	31.8	0.9	---	---	---
	T651 (417)	PLATE	1.50-3.93	1.50	36.0	3.4	1.49	29.4	1.8	1.00	26.6	1.8
2219	T851	PLATE	1.00-3.25	0.97	33.4	2.3	0.75	29.7	3.2	0.50	23.0	2.4
		FORGING	---	---	---	---	---	---	---	1.00	25.6	3.1
	T852	FORGING	2.00-7.50	1.50	39.2	3.2	1.50	27.1	2.2	0.75	25.3	3.1
2419	T87	PLATE	1.00-2.00	1.00	28.0	3.0	0.97	22.0	0.4	---	---	---
	T87-300F 100HRS	PLATE	1.50	1.47	34.8	0.4	---	---	---	---	---	---
	T651	PLATE	1.75-3.00	1.50	42.6	5.3	1.40	37.2	4.2	1.00	24.8	2.5
2618	T651	PLATE	3.34	---	---	---	---	---	---	1.00	14.9	1.2
	T651	PLATE	1.50-2.50	---	---	---	1.00	26.6	0.9	1.00	21.5	0.4

* MINIMUM SPECIMEN THICKNESS (IN)

TABLE 7.0.3.1

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS OF
2000 AND 6000 SERIES ALUMINUM ALLOYS (WITH BUCKLING CONSTRAINTS)

ALLOY	CONDITION/HT	TEST TEMP., (°F)	SPECIMEN ORIENT	SPECIMEN WIDTH	YIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN.) = 0.063	K _c (KSI √IN.)		
							0.100	0.125	0.200
2014	T6	-320	L-T	4.0	74.1	59.2/1.1(2)			
			L-T	18.0	74.1	74.2/3.2(4)			
	R. T.	L-T	16.0	68.4	65.0/3.4(5)				
		T-L	3.0	65.2	72.0/3.4(5)				
	-320	L-T	6.0	75.9	46.6/5.3(9)				
		T-L	12.0	75.9	48.3/4.6(5)				
	T3	R. T.	L-T	30.0	51.9	108.9/8.2(3)			
		R. T.	T-L	6.0	57.0		63.0/1.4(2)		
	T62(QQ)	R. T.	L-T	6.0	---		77.1/5.8(2)		
		R. T.	T-L	16.0	---		139.2		
T81	R. T.	L-T	6.0	---		72.4/2.1(2)			
	R. T.	T-L	6.0	64.8		65.4/3.8(2)			
2124	T851	R. T.	T-L	5.8	55.0			50.9/2.0(4)	
			T-L	5.8	55.0				
2219	T87	-423	L-T	16.0	73.8	90.6/3.2(2)			
			L-T	24.0	58.5		90.6/15.0(6)		
		R. T.	L-T	48.0	58.5		109.8/12.1(7)		
			L-T	48.0	58.5				

Mean/Standard Deviation (Number of Specimens)

TABLE 7.0.3.2
 PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS
 OF 2000 AND 6000 SERIES ALUMINUM ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

ALLOY	CONDITION/H.T.	TEST TEMP. (°F)	SPECIMEN ORIENT	SPECIMEN WIDTH	YIELD STRENGTH (Ksi)	SPECIMEN THICKNESS (IN.) = 0.063	0.127	0.250	0.400	1.000	K_c (Ksi $\sqrt{in.}$)	
2014	T6	-423	T-L	4.0	31.8	59.1/3.5(5)						
		R. T.	T-L	15.8	65.4	58.4/2.7(5)						
2020	T6	R. T.	L-T	2.0	76.5	34.6/7.0(5)						
				3.0	75.9	30.2/1.3(2)						
		T-L		15.8	76.9	36.9/2.9(4)						
				2.0	75.9	30.5/6.6(5)						
				3.0	75.8	27.8/0.8(2)						
	15.8	75.6	34.5/2.0(5)									
2020(Alclad)	T6	R. T.	L-T	3.0	76.3	41.3/2.7(12)	26.4/0.3(3)					
				4.0	77.4	24.2/2.3(3)						
		T-L		20.0	76.3							30.5/2.5(11)
				3.0	77.5	23.5/2.4(12)	17.2/2.6(3)					
				4.0	78.0	20.9/0.1(2)						19.4/0.8(12)
	20.0	78.0										
2020(Alclad)	T6	R. T.	L-T	15.8	68.0	34.1/1.8(2)						
				3.0	68.6	40.2/3.3(7)						
		T-L		15.8	67.2	33.9/1.2(2)						
				3.0	68.4	30.4/5.0(7)						

Mean/Standard Deviation (Number of Specimens)

TABLE 7.0.3.2 (con't)

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS
OF 2000 AND 6000 SERIES ALUMINUM ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

ALLOY	CONDITION/H.T.	TEST TEMP. (°F)	SPECIMEN ORIENT	SPECIMEN WIDTH	YIELD STRENGTH (Ksi)	SPECIMEN THICKNESS (IN.) = 0.063	K _c (Ksi √In.)			
							0.127	0.250	0.400	1.000
2024	T351 31	R. T.	L-T	20.0	58.2	57.9/3.2(2) 61.2/5.1(3) 54.6/0.0(2) 54.6/0.7(2) 55.9/2.9(2) 52.2/0.9(2)	107.1/1.8(2)	44.8/1.7(9)	31.3/2.5(6) 47.1/8.1(7)	68.9/2.3(2)
		R. T.	T-L	6.0	62.0					
			9.0	62.0						
			15.0	62.0						
			18.0	62.0						
			21.0	62.0						
T851	R. T.	L-T	20.0	66.0	48.4/3.8(12)					
		T-L	3.0	65.4						
			4.0	66.2						
T86	R. T.	L-T	15.8	72.9	33.7/1.9(12)					
		T-L	2.0	71.6						
			15.8	71.2						
2124	T851	R. T.	L-T	6.0	55.0	68.9/2.3(2)				
			T-L	3.0	59					
2219	T851	R. T.	L-T	20.0	51.1	84.7/9.0(10)				
			T-L	20.0	50.2					
T87	R. T.	L-T	16.0	57.7	75.9/1.1(2)	66.3/4.2(12)				

Mean/Standard Deviation (Number of Specimens)

TABLE 7.0.4.1

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION L-T ENVIRONMENT LAB AIR AT R. T.
 STRESS RATIO: 0.00-0.10 FREQUENCY: 0.10-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =		
					2.5	5.0	10.0
2014	T6	SHEET	0.05	2.00		6.41	
2020	T6	SHEET	0.00	13.30		104	
	T651	PLATE	0.00	5.20		3.45	
2024	T3	SHEET	0.00	13.30		28.6	
	T3	PLATE	0.05	20.00		4.36	
	T351	SHEET	0.00	3.00- 6.00		6.16	44.0
	T351	PLATE	0.00	1.00- 16.00			2324
	T351	PLATE	0.00	5.00- 20.00	156		
	T351	PLATE	0.01	1.00- 10.00	205	7.09	39.8
	T351	PLATE	0.01	20.00		5.98	52.1
	T351	PLATE	0.10	3.00			55.0
	T351	PLATE	0.10	20.00		8.62	
	T3511	EXTRUSION	0.05	9.00	129		
2124	T42	PLATE	0.02	10.00		4.25	23.6
	T81	SHEET	0.05	2.00		8.08	68.1
	T851	PLATE	0.02	1.00- 10.00		3.92	57.0
T851	PLATE	0.02	1.00- 30.00	0.074	272	3.84	56.7

TABLE 7.0.4.1 (con't)

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION: L-T ENVIRONMENT: LAB AIR AT R. T.
 STRESS RATIO 0.00-0.10 FREQUENCY: 0.10-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =					
					2.5	5.0	10.0	20.0	50.0	100.0
2219	T851	PLATE	0.00	5.20			8.25	54.8		
	T851	PLATE	0.00	6.00			4.33	34.6		
	T851	PLATE	0.01	3.00				44.5	1622	
	T851	PLATE	0.01	6.00				46.2	1788	
	T851	PLATE	0.01	1.00-20.00				44.9		
	T851	PLATE	0.04	1.00-20.00			4.24			
	T851	PLATE	0.05	1.00-20.00			2.46	33.9		
	T851	PLATE	0.05	1.00-20.00			3.58			
	T851	PLATE	0.05	1.00-20.00			5.14	48.3		
	T851	PLATE	0.08	6.00			5.74	44.9		
2419	T851	PLATE	0.10	30.00			6.30	53.9		
6061	T651	PLATE	0.00	10				57.4		

TABLE 7.0.4.2

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS.

SPECIMEN ORIENTATION T-L ENVIRONMENT LAB AIR AT R T
 STRESS RATIO 0.00-0.10 FREQUENCY 0.10-30.00 HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS
					2.5 5.0 10.0 20.0 50.0 100.0
2014	T6	SHEET	0.05	2.00	
	T6	FORGING	0.05	30.00	
2024	T3	SHEET	0.00	13.30	
	T3	SHEET	0.05	30.00	
	T861	SHEET	0.08	10-15.00	
	T861	SHEET	0.10	4.0	
	T861	SHEET	0.10	10-15.00	
	T861	SHEET	0.10	10-15.00	
	T861	SHEET	0.10	10-15.00	
	T861	SHEET	0.10	10-15.00	
	T861	SHEET	0.10	10-15.00	
	T861	SHEET	0.10	10-15.00	
2419	T861	PLATE	0.10	10-15.00	
	T861	PLATE	0.10	10-15.00	
	T861	PLATE	0.10	10-15.00	

TABLE 7.0.5

STRESS CORROSION CRACKING THRESHOLD DATA FOR 2000 AND 6000
SERIES ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/HT	PRODUCT FORM	SPECIMEN ORIENTATION	ENVIRONMENTS							K _{Isc} (Ksi $\sqrt{\text{in.}}$)									
				INDUSTRIAL ATMOSPHERE	SEACOAST ATMOSPHERE	SUMP TANK WATER	3.5% NaCl	DICHROMATE ACETATE	SYNTHETIC SEAWATER	SHOP CLEANING SOLVENT										
				7.0	7.0			7.0	16.0											
2014	T6	F	S-L																	
	T651	P	S-L	7.0	7.0															
2020	T651	P	S-L																	
2021	T81	P	S-L	19.0	19.0															
	T81-Overheated Weld	P	S-L																	
	T81-Repaired Weld-Aged 16HR	P	S-L																	
	325F-Weld Fusion Line																			
	T81-Repaired Weld-Aged 16HR 325F-Heat Affected Zone	P	S-L																	
	T81-Welded Aged 16HR 325F Weld Center Line	P	S-L																	
	T81-Welded Aged 16HR 325F Heat Affected Zone	P	S-L																	
	T81-Welded Aged 16HR 325F Fusion Line	P	S-L																	

TABLE 7.0.5 (con't)

STRESS CORROSION CRACKING THRESHOLD DATA FOR 2000 AND 6000 SERIES ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/HT	PRODUCT FORM	SPECIMEN ORIENTATION	ENVIRONMENTS					K _{Iacc} (Ksi $\sqrt{in.}$)
				INDUSTRIAL ATMOSPHERE	SEACOAST ATMOSPHERE	SUMP TANK WATER	3.5% NaCl	SALT DICHROMATE ACETATE	
2024	T351	P	S-L	10.0	10.0		10.0	9.0	
	T851	P	L-T				21.5		
	T852	F	L-T T-L S-L	16.0	16.0			15.0	28.1(2)
2124	T851	L-T S-L						26.6(3) 22.7(3)	
	T37 T851	P P	S-L L-T	13.0	13.0			9.0	34.3(3)
6061	T87	P	S-L	19.0	19.0		34.5(2) 27.0	19.0	
	T651	P	S-L	20.0	20.0			20.0	

TABLE 7.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 2014 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SORT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
PLATE		
T651	23.3 ± 1.0 (10)	21.4 ± 1.2 (19) 17.8 ± 0.1 (2)
FORGING		
T6	27.9 ± 0.8 (2)	17.4 ± 1.7 (4) 16.9 ± 1.9 (5)
T611	-----	----- 17.8 ± 0.6 (2)
T652	28.8 ± 3.6 (12)	21.9 ± 3.2 (13) 18.1 ± 1.4 (3)
EDGED BAR		
T6	-----	16.7 ± 0.6 (2) -----

TABLE 7.1.1.2
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 ALUMINUM 2014

TEST CONDITIONS		ENVIRONMENT		FATIGUE CRACK GROWTH RATES				
SPECIMEN ORIENTATION	LAB AIR AT R T	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)				
T6	SHEET	0.05	2.00			6.41		
T6	SHEET	0.25	2.00			9.59		
T6	SHEET	0.40	2.00		1.37	13.5		
T6	SHEET	0.50	2.00		1.57			
T6	SHEET	0.57	2.00		1.02			

TABLE 7.1.1.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 2014

TEST CONDITIONS

SPECIMEN ORIENTATION T-C

ENVIRONMENT LAB AIR AT R 1

CONDITION/HI	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))		FATIGUE CRACK GROWTH RATES (MICR/100CYCLE)			
				2.5	5	10	20	50	100
T6	SHEET	0.05	2.00						7.03
T6	SHEET	0.25	2.00						11.0
T6	SHEET	0.40	2.00				1.29		16.3
T6	SHEET	0.50	2.00				1.59		
T6	SHEET	0.57	2.00				1.25		
T6	FORGING	0.05	--						1.49

TABLE 7.1.1.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2014

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT H H A
A I R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICR IN/CYCLE)
				2.5 5 10 20 50 100	
T6	FORGING	0.05			1.20 22.0
T6	FORGING	-1.00	9.00		1.26 17.4

TABLE 7.1.2.1

CONDITION	--PRODUCT--		YIELD STRENGTH (KSI)	SPECIMEN		DESIGN	K(1C)		2.5* CRACK LENGTH (IN)	K(1C)/TYB)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER	
	FORM	THICK (IN)		THICK (IN)	WIDTH (IN)		THICK (IN)	K(1C)							K(1C)
T6	F	0.89	63.8	1.500	0.714	NB	0.778	0.50	28.50	27.30	27.9/	0.8	1973	86213	
		0.89	63.8	1.500	0.713	NB	0.778	0.46					1973	86213	
T6	F	0.89	62.4	0.500	0.249	NB	0.266	0.15	15.50	15.50			1973	86213	
		0.89	62.4	0.500	0.249	NB	0.269	0.17	16.50	16.50			1973	86213	
		0.89	63.0	0.490	0.249	NB	0.258	0.23	19.20	19.20			1973	86213	
		0.89	63.0	0.500	0.249	NB	0.266	0.21	18.20	18.20	17.4/	1.7	1973	86213	
T6	F	0.89	62.4	1.500	0.750	CT	0.753	0.14	14.90	14.90			1973	86213	
T6	F	8.00	61.0	2.000	1.000	NB	1.000	0.24	19.10	19.10			1972	82675	
		8.00	61.0	2.000	1.000	NB	---	0.24	19.10	19.10			1972	82675	
		8.00	61.0	2.000	1.000	NB	1.000	0.24	19.00	19.00			1972	82675	
		8.00	61.0	2.000	1.000	NB	---	0.24	19.00	19.00	19.1/	0.1	1972	82675	
T6	F	8.00	61.0	1.000	1.000	NB	0.500	0.18	16.40	16.40			1972	82675	
		8.00	61.0	1.000	1.000	NB	---	0.17	15.70	15.70			1972	82675	
		8.00	61.0	1.000	1.000	NB	0.500	0.17	15.70	15.70			1972	82675	
		1.00	63.8	1.500	0.749	CT	0.778	0.25	20.30	20.30	16.9/	1.9	1973	86213	
T6	F	---	63.8	1.500	0.750	NB	0.750	0.50	28.50	28.50			1972	82879	
		---	63.8	1.500	0.750	NB	0.750	0.46	27.30	27.30	27.9/	0.8	1972	82879	
T6	F	---	62.7	0.500	0.250	NB	0.250	0.21	18.20	18.20			1972	82879	
		---	62.7	0.500	0.250	CT	0.750	0.14	15.10	15.10			1972	82879	
		---	62.7	0.500	0.250	CT	0.750	0.13	14.30	14.30			1972	82879	
		---	62.7	0.500	0.250	NB	0.250	0.23	19.20	19.20	16.7/	2.4	1972	82879	
T6	FB	4.50	64.2	1.490	0.689	NB	0.737	0.49	28.40	28.40			1973	86213	
T6	FB	4.50	62.4	0.500	0.249	NB	0.258	0.17	17.10	17.10			1973	86213	
		4.50	62.4	0.500	0.249	NB	0.267	0.17	16.30	16.30	16.7/	0.6	1973	86213	
T6	FB	4.50	62.4	1.500	0.749	CT	0.762	0.19	17.40	17.40			1973	86213	
T6	FB	4.50	62.4	1.500	0.750	CT	0.783	0.21	17.90	17.90			1973	86213	
		4.50	62.4	1.500	0.751	CT	0.749	0.18	16.60	16.60	17.3/	0.9	1973	86213	

TABLE 7.1.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	THICKNESS (IN)	TEMP (F)	SPECIMEN		WIDTH (IN)	THICKNESS (IN)	DESIGN	CRACK LENGTH (IN)	2.5* CRACK LENGTH (IN)	K(1C)/TYS)**2	K(1C) MEAN (KSI*SQRT IN)	STAN	DATE	REFER			
	FORM	PRODUCT					H	B											A	K(1C)	K(1C)
T61	F	1.50	56.6	R-T	1.00	0.500	CT	0.486	0.31	19.90	19.90	0.0	19.90	19.90	19.90	19.90	19.90	19.90			
	F	1.50	56.6		1.000	0.500	CT	0.508	0.31	19.90	19.90	0.0	19.90	19.90	19.90	19.90	19.90	19.90			
T61	F	1.95	62.4	S-L	1.000	0.499	CT	0.491	0.22	18.70	18.70	0.7	18.70	18.70	18.70	18.70	18.70	18.70			
	F	1.95	62.4		1.000	0.499	CT	0.479	0.20	17.70	17.70	0.7	17.70	17.70	17.70	17.70	17.70	17.70			
T611	F	1.00	60.2	R-T	1.490	0.750	CT	0.783	0.23	18.20	18.20	0.6	18.20	18.20	18.20	18.20	18.20	18.20			
	F	1.00	60.2		1.490	0.749	CT	0.771	0.21	17.30	17.30	0.6	17.30	17.30	17.30	17.30	17.30	17.30			
T611	F	1.00	61.3	S-L	1.500	0.749	CT	0.778	0.24	19.00	19.00	0.2	19.00	19.00	19.00	19.00	19.00	19.00			
	F	1.00	61.3		1.500	0.749	CT	0.767	0.23	18.60	18.60	0.2	18.60	18.60	18.60	18.60	18.60	18.60			
	F	1.00	62.0		1.500	0.747	CT	0.797	0.22	18.50	18.50	0.2	18.50	18.50	18.50	18.50	18.50	18.50			
	F	1.00	62.0		1.500	0.749	CT	0.802	0.23	18.80	18.80	0.2	18.80	18.80	18.80	18.80	18.80	18.80			
T651	P	1.50	66.7	L-S	1.000	0.500	CT	0.490	0.31	23.40	23.40	0.9	23.40	23.40	23.40	23.40	23.40	23.40			
	P	1.50	66.7		1.000	0.499	CT	0.503	0.33	24.10	24.10	0.9	24.10	24.10	24.10	24.10	24.10	24.10			
T651	P	5.00	58.6	R-T	2.000	0.999	NB	0.975	0.37	22.40	22.40	1.0	22.40	22.40	22.40	22.40	22.40	22.40			
	P	2.50	64.4		1.990	1.001	CT	0.970	0.33	23.30	23.30	1.0	23.30	23.30	23.30	23.30	23.30	23.30			
	P	2.50	64.4		2.000	1.000	CT	0.966	0.34	23.60	23.60	1.0	23.60	23.60	23.60	23.60	23.60	23.60			
	P	1.00	66.4		2.000	1.020	NB	0.966	0.35	24.70	24.70	1.0	24.70	24.70	24.70	24.70	24.70	24.70			
	P	1.00	66.4		2.000	1.018	NB	0.970	0.32	23.60	23.60	1.0	23.60	23.60	23.60	23.60	23.60	23.60			
	P	1.00	66.4		2.000	1.019	NB	0.961	0.35	24.80	24.80	1.0	24.80	24.80	24.80	24.80	24.80	24.80	24.80		
	P	1.00	66.4		2.000	1.020	NB	1.000	0.33	24.00	24.00	1.0	24.00	24.00	24.00	24.00	24.00	24.00	24.00		
	P	1.75	68.4		2.000	0.999	NB	0.957	0.26	21.90	21.90	1.0	21.90	21.90	21.90	21.90	21.90	21.90	21.90		
	P	1.75	68.4		2.000	0.998	NB	0.960	0.27	22.40	22.40	1.0	22.40	22.40	22.40	22.40	22.40	22.40	22.40		
	P	1.75	68.4		1.990	0.999	NB	0.960	0.27	22.30	22.30	1.0	22.30	22.30	22.30	22.30	22.30	22.30	22.30		
	P	1.00	62.7	L-T	2.000	1.001	CT	1.006	0.39	24.90	24.90	1.0	24.90	24.90	24.90	24.90	24.90	24.90	24.90		
T651	P	1.00	63.5		2.000	1.002	CT	0.966	0.26	20.30	20.30	1.0	20.30	20.30	20.30	20.30	20.30	20.30			
	P	1.00	66.4		2.000	1.002	CT	0.973	0.29	22.50	22.50	1.0	22.50	22.50	22.50	22.50	22.50	22.50			
	P	1.00	66.4		2.000	1.002	CT	0.949	0.30	23.00	23.00	1.0	23.00	23.00	23.00	23.00	23.00	23.00			
	P	1.00	66.4		2.000	1.002	CT	0.960	0.29	22.70	22.70	1.0	22.70	22.70	22.70	22.70	22.70	22.70			
T651	P	1.50	66.7	L-T	1.000	0.501	CT	0.499	0.21	19.20	19.20	1.0	19.20	19.20	19.20	19.20	19.20	19.20	19.20		

TABLE 7.1.2.1 (Con't)

CONDITION	ALUMINUM										K(1C)	K(1C) STAN DEV	DATE	REFER		
	---PRODUCT---		TEST SPECIMEN		YIELD STRENGTH		---SPECIMEN---		CRACK						2.5*	
	FORM	THICK (IN)	THICK (IN)	TEMP (F)	ORIENT	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)	(K(1C)/TYS)**2						
T651	P	1.50	88	L-T	66.7	1.000	0.501	CT	0.495	0.21	19.50	19.3/	0.2	1973	86213	
		1.50			66.7	1.000	0.501	CT	0.491	0.21	19.50			1973	86213	
T651	P	1.50	88	T-S	63.2	1.000	0.500	CT	0.504	0.33	22.80			1973	86213	
		1.50			63.2	1.000	0.500	CT	0.506	0.30	21.80			1973	86213	
		1.50			63.2	1.000	0.501	CT	0.510	0.32	22.50	22.4/	0.5	1973	86213	
T651	P	1.00	-320	T-L	75.0	2.000	1.020	NB	1.010	0.30	26.10	26.1/	0.0	1971	84288	
		1.00			75.0	2.000	1.018	NB	1.008	0.30	26.10			1973	86213	
T651	P	5.00	R.T.	T-L	57.8	2.000	1.000	NB	0.997	0.27	19.10			1973	86213	
		1.00			65.8	2.000	1.016	NB	0.981	0.23	20.10			1973	86213	
		1.00			65.8	2.000	1.016	NB	0.960	0.24	20.20			1973	86213	
		1.00			65.8	2.000	1.016	NB	0.989	0.26	20.90			1971	84288	
		1.00			65.8	2.000	1.016	NB	0.985	0.26	20.90			1971	84288	
		1.00			65.8	2.000	1.022	NB	1.008	0.27	21.80			1973	86213	
		1.00			65.8	1.990	1.023	NB	1.000	0.28	22.00			1973	86213	
		1.00			65.8	2.000	1.016	NB	0.966	0.24	20.30			1973	86213	
		1.00			65.8	2.000	1.000	CT	1.084	0.26	21.20			1973	86213	
		1.00			65.8	2.000	1.016	NB	0.970	0.25	21.00			1971	84288	
		1.00			65.8	2.000	1.023	NB	0.980	0.28	21.90			1973	86213	
		1.00			65.8	2.000	1.022	NB	1.023	0.29	22.30			1973	86213	
		1.00			65.8	2.000	1.023	NB	0.997	0.28	22.10			1973	86213	
		1.00			65.8	2.000	1.016	NB	0.961	0.25	20.70			1973	86213	
		1.00			65.8	2.000	1.016	NB	1.001	0.24	20.70			1971	84288	
		1.00			65.8	2.000	1.016	NB	0.998	0.29	22.60			1971	84288	
		1.75			66.2	2.000	0.997	NB	1.058	0.32	23.60			1973	86213	
		1.75			66.2	2.000	1.000	NB	0.980	0.29	22.50			1973	86213	
		1.75			66.2	2.000	1.000	NB	1.010	0.32	23.60	21.4/	1.2	1973	86213	
T651	P	1.00	84	T-L	63.5	2.000	1.002	CT	0.981	0.27	20.70			1973	86213	
		1.00			65.8	2.000	1.000	CT	0.984	0.22	19.50			1973	86213	
		1.00			65.8	2.000	1.001	CT	0.978	0.23	20.00			1973	86213	
		1.00			65.8	2.000	1.001	CT	0.964	0.22	19.60	20.0/	0.5	1973	86213	
T651	P	1.50	88	T-L	63.2	1.000	0.500	CT	0.500	0.22	18.70			1973	86213	
		1.50			63.2	1.000	0.500	CT	0.519	0.24	19.70	19.2/	0.7	1973	86213	
T651	P	5.00	R.T.	5-L	55.0	1.000	0.501	NB	0.529	0.26	17.90			1973	86213	

TABLE 7.1.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	SPECIMEN THICK (IN)	DESIGN THICK (IN)	CRACK LENGTH (IN)	2.5* (K(IC)/TYS)**2 (IN)	K(IC) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER		
	FORM	THICK (IN)												
	W	B												
T651	P	5.00	55.0	R.T.	1.000	0.498	NB	0.522	0.26	17.70	17.8/	0.1	1973	86213
T652	F	5.00	60.7	R.T.	3.000	1.500	NB	1.498	0.62	30.20			1970	77720
		5.00	60.7		3.000	1.500	NB	1.460	0.54	28.20			1970	77720
		4.00	62.5		3.000	1.502	NB	1.485	0.75	29.20			1970	77720
		4.00	62.5		3.000	1.502	NB	1.577	0.80	34.20			1970	77720
		4.00	62.5		3.000	1.502	NB	1.442	0.69	35.40			1970	77720
		3.00	66.2		2.000	1.000	NB	0.925	0.39	32.80			1970	77720
		3.00	66.2		2.000	1.000	NB	0.970	0.40	26.30			1970	77720
		3.00	66.2		2.000	1.000	NB	0.968	0.42	26.50			1970	77720
		2.00	66.5		1.500	0.750	NB	0.688	0.39	27.10			1970	77720
		2.00	66.5		1.500	0.752	NB	0.728	0.33	24.90			1970	77720
		2.00	66.5		1.500	0.751	NB	0.752	0.41	24.30	28.8/	3.6	1970	77720
T652	F	5.00	57.3	R.T.	3.000	1.500	NB	1.662	0.24	17.90			1970	77720
		5.00	57.3		3.000	1.500	NB	1.597	0.33	20.70			1970	77720
		5.00	57.3		3.000	1.500	NB	1.612	0.31	20.10			1970	77720
		6.00	57.7		4.000	2.005	NB	2.092	0.49	25.40			1970	77720
		6.00	57.7		4.000	2.004	NB	2.215	0.39	22.80			1970	77720
		6.00	57.7		4.000	2.003	NB	1.987	0.66	29.80			1970	77720
		4.00	59.2		3.000	1.502	NB	1.562	0.37	22.70			1970	77720
		4.00	59.2		3.000	1.502	NB	1.497	0.38	23.00			1970	77720
		4.00	59.2		3.000	1.502	NB	1.642	0.40	23.70			1970	77720
		2.00	64.9		1.500	0.754	NB	0.748	0.22	19.20			1970	77720
		2.00	64.9		1.500	0.753	NB	0.727	0.22	19.30			1970	77720
		3.00	65.1		2.000	0.999	NB	1.020	0.24	20.30			1970	77720
		3.00	65.1		1.990	0.999	NB	1.025	0.22	19.50	21.9/	3.2	1970	77720
T652	F	5.00	56.1	R.T.	1.000	0.500	NB	0.467	0.29	17.80			1970	77720
		5.00	56.1		1.000	0.501	NB	0.470	0.31	19.60			1970	77720
		5.00	56.1		1.000	0.498	NB	0.510	0.22	16.80	18.1/	1.4	1970	77720

TABLE 7.1.2.2

ALUMINUM		2014		K(C)											
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	CRACK LENGTH OR GROSS STRESS		K(AFP) MEAN DEV (KSI*SQRT IN)	K(C) MEAN DEV (KSI*SQRT IN)	STAN DEV	DATE	REFER					
				W	R						INIT (IN)	FINAL (IN)	MAX (KSI)		
T6	8	0 06	- 423	L-T	83.4	4.000	0.062	1.220	1.700	---	41.80	61.43	77.08*	1963	51527
		0 06			83.4	4.000	0.062	1.240	1.620	---	42.00	62.35	74.70*	1963	51527
		0 06			83.4	4.000	0.063	1.230	1.650	---	40.50	59.82	73.02*	1963	51527
		0 06			83.4	4.000	0.062	1.200	1.700	---	36.10	54.95	66.57	1963	51527
T6	8	0 06	- 320	L-T	74.1	3.950	0.062	1.230	1.660	---	40.70	60.21	73.95*	1963	51527
		0 06			74.1	3.990	0.063	1.230	1.420	---	37.00	54.67	60.02	1963	51527
		0 06			74.1	3.990	0.063	1.230	1.740	---	39.80	58.80	74.77*	1963	51527
		0 06			74.1	3.990	0.063	1.240	---	---	38.20	56.73	---	1963	51527
T6	8	0 06	- 320	L-T	74.1	3.990	0.063	1.230	1.410	---	36.20	53.49	58.44	1963	51527
		0 06			74.1	18.040	0.063	3.490	7.300	---	19.40	60.46	73.23	1963	51527
		0 06			74.1	18.040	0.063	3.480	7.100	---	19.40	60.39	71.77	1963	51527
		0 06			74.1	18.040	0.064	3.480	6.980	---	19.90	61.95	72.73	1963	51527
T6	8	0 06	R. T.	L-T	66.2	2.000	0.067	0.625	0.980	---	20.70	64.43	78.91	1963	51527
		0 06			67.5	2.000	0.064	0.625	0.770	---	38.10	40.16*	55.78*	1973	86213
		0 06			67.5	2.000	0.065	0.620	0.860	---	38.60	40.68*	56.01*	1973	86213
		0 06			67.5	2.000	0.064	0.625	1.020	---	40.10	42.09*	52.76*	1973	86213
T6	8	0 06	R. T.	L-T	65.2	3.980	0.063	1.240	1.600	---	38.10	56.60*	67.23*	1963	51527
		0 06			65.2	3.990	0.063	1.240	1.540	---	38.20	56.73*	65.94*	1963	51527
		0 06			65.2	3.990	0.063	1.230	1.940	---	36.90	54.52*	63.31*	1963	51527
		0 06			65.2	4.000	0.063	1.230	1.550	---	37.80	55.85*	65.19*	1963	51527
T6	8	0 06	R. T.	L-T	68.4	15.810	0.063	6.000	7.020	---	16.40	55.35	62.20	1973	86213

*NOTE - NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD DEV

TABLE 7.1.2.2 (Con't)

CONDITION	ALUMINUM	2014	K(C)	CRACK LENGTH CROSS STRESS										K(APP) STAN			K(C) STAN		
				---SPECIMEN---		INIT		FINAL		ONSET		MAX		K(APP)		K(C)		K(C)	
				FORM	THICK	W	THICK	INIT	FINAL	ONSET	ONSET	ONSET	ONSET	MAX	MAX	MEAN	DEV	MEAN	DEV
T6	S	0 06	R T	L-T	68 4	15 810	0 064	3 010	3 570	---	27 40	60 95	67 00	1973	86213				
		0 06			68 4	15 810	0 064	4 000	5 230	---	22 50	58 73	69 22	1973	86213				
		0 06			68 4	15 820	0 064	6 000	7 000	---	16 10	54 33	60 92	1973	86213				
		0 06			68 4	15 820	0 064	1 000	1 520	---	42 10	52 89	56 5/ 3 3	65 43	65 0/ 3 4	1973	86213		
T6	S	0 06	R T	L-T	65 2	18 040	0 063	5 490	6 350	---	20 70	64 31	70 87	1963	51527				
		0 06			65 2	18 040	0 063	5 490	6 110	---	20 60	64 20	68 75	1963	51527				
		0 06			65 2	18 050	0 063	5 490	6 400	---	20 80	64 82	71 58	1963	51527				
		0 06			65 2	18 060	0 063	5 490	6 800	---	21 70	67 62	77 84	1963	51527				
		0 06			65 2	18 060	0 063	5 480	6 300	---	20 80	64 74	65 2/ 1 4	70 82	72 0/ 3 4	1963	51527		
T6	S	0 06	- 320	T-L	75 9	3 000	0 058	0 130	0 210	---	63 70	28 82*	36 70*	1967	68908				
		0 06			75 9	3 000	0 058	0 130	0 160	---	63 30	28 64*	31 79*	1967	68908				
		0 06			75 9	3 000	0 058	0 300	0 410	---	49 90	34 47	40 51	1967	68908				
		0 06			75 9	3 000	0 059	0 300	0 430	---	49 70	34 33	41 37	1967	68908				
		0 06			75 9	3 000	0 059	0 300	0 420	---	50 40	34 81	41 44	1967	68908				
		0 06			75 9	3 000	0 061	0 500	0 850	---	43 40	39 13	52 79	1967	68908				
		0 06			75 9	3 000	0 061	0 130	0 190	---	66 50	30 09*	36 42*	1967	68908				
		0 06			75 9	3 000	0 060	1 400	1 400	---	30 50	41 08	52 47	1967	68908				
		0 06			75 9	3 000	0 061	0 500	0 580	---	42 10	37 96	41 14	1967	68908				
		0 06			75 9	3 000	0 061	1 010	1 300	---	30 40	41 21	49 28	1967	68908				
		0 06			75 9	3 000	0 060	0 500	0 730	---	44 20	39 86	49 14	1967	68908				
		0 06			75 9	3 010	0 061	1 000	1 390	---	29 90	40 29	38 1/ 2 9	51 08	46 6/ 5 3	1967	68908		
T6	S	0 06	- 320	T-L	75 9	6 000	0 061	0 130	0 200	---	64 90	29 34*	36 40*	1967	68908				
		0 06			75 9	6 000	0 060	0 130	0 200	---	66 80	30 19*	37 47*	1967	68908				
		0 06			75 9	6 000	0 061	0 250	0 380	---	56 20	35 26	43 53	1967	68908				
		0 06			75 9	6 000	0 061	0 250	0 370	---	56 50	35 44	43 17	1967	68908				
		0 06			75 9	6 000	0 060	0 130	0 180	---	65 90	29 79*	35 06*	1967	68908				
		0 06			75 9	6 000	0 061	2 000	2 540	---	22 30	42 47	50 21	1967	68908				
		0 06			75 9	6 000	0 061	2 000	2 550	---	22 10	44 00	51 72	1967	68908				
		0 06			75 9	6 000	0 061	2 000	2 580	---	23 90	43 62	52 64	1967	68908				
		0 06			75 9	6 000	0 061	0 250	0 400	---	56 80	35 63	39 4/ 4 4	45 15*	48 3/ 4 6	1967	68908		
T6	S	0 06	- 320	T-L	75 9	12 000	0 059	0 260	0 400	---	57 50	36 76	45 61	1967	68908				

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 7.1.2.2 (Con't)

CONDITION	ALUMINUM		2014		K(C)		CRACK LENGTH CROSS STRESS				K(APP) STAN		K(C) STAN					
	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR	YIELD STR (KSI)	--SPECIMEN--		INIT (IN)	FINAL (IN)	DNSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	MEAN (IN)	DEV (IN)	K(C) (KSI*SQRT IN)	MEAN (IN)	DEV (IN)	DATE	REFER
					WIDTH (IN)	THICK B												
T6	S	0.06	- 320	T-L	75.9	12.000	0.059	0.130	0.240	---	45.20	29.47*	---	40.04*	---	---	---	1967 68908
		0.06			75.9	12.000	0.058	0.500	0.910	---	43.50	38.59	---	52.19	---	---	---	1967 68908
		0.06			75.9	12.000	0.058	0.500	0.690	---	44.50	39.48	---	46.42	---	---	---	1967 68908
		0.06			75.9	12.000	0.058	0.500	0.690	---	43.40	38.50	---	45.28	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	0.250	0.450	---	56.30	35.29	---	47.38	---	---	---	1967 68908
		0.06			75.9	12.000	0.061	2.000	2.220	---	25.10	45.27	---	47.89	---	---	---	1967 68908
		0.06			75.9	12.000	0.061	1.000	1.610	---	29.10	36.63	---	46.80	---	---	---	1967 68908
		0.06			75.9	12.000	0.061	1.000	1.560	---	33.30	41.92	---	52.68	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	2.000	2.610	---	27.60	49.78	---	57.57	---	---	---	1967 68908
		0.06			75.9	12.000	0.061	4.000	4.760	---	17.30	46.60	---	52.49	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	0.130	0.240	---	65.80	29.74*	---	40.41*	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	0.130	0.250	---	66.20	29.92*	---	41.90*	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	4.000	4.650	---	17.00	45.79	---	50.72	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	1.000	1.530	---	35.30	44.43	---	55.28	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	4.000	4.920	---	16.70	44.98	---	51.92	---	---	---	1967 68908
		0.06			75.9	12.000	0.060	4.000	4.800	---	15.90	42.83	---	48.54	---	---	---	1967 68908
		0.06			75.9	12.010	0.059	0.250	0.440	---	53.90	33.79	41.4/ 4.7	44.85	49.7/ 3.9	---	---	1967 68908

BUCKLING OF CRACK EDGES RESTRAINED

BUCKLING OF CRACK EDGES NOT RESTRAINED

T6	S	0.12	R. T.	L-T	64.0	3.000	0.126	1.120	1.760	---	33.30	48.40*	---	71.21*	---	---	---	1973 86213
		0.12			64.0	3.000	0.126	1.090	1.900	---	34.90	49.78*	---	81.70*	---	---	---	1973 86213
T6	P	0.25	R. T.	L-T	65.0	3.000	0.247	1.100	1.720	---	31.60	45.36	---	65.90*	---	---	---	1973 86213
		0.25			65.0	3.000	0.247	1.220	1.810	---	29.20	45.11	45.2/ 0.2	64.45*	---	---	---	1973 86213
T6	S	0.06	- 423	T-L	81.8	4.000	0.063	1.230	1.370	---	36.00	53.17	---	56.99	---	---	---	1963 51527
		0.06			81.8	4.000	0.063	1.210	1.550	---	36.30	53.07	---	62.53	---	---	---	1963 51527
		0.06			81.8	4.000	0.063	1.230	1.250	---	37.80	53.83	---	56.40	---	---	---	1963 51527
		0.06			81.8	4.000	0.064	1.230	1.620	---	35.60	52.58	---	63.32	---	---	---	1963 51527
		0.06			81.8	4.000	0.063	1.230	1.450	---	34.30	50.66	53.1/ 1.8	56.41	59.1/ 3.9	---	---	1963 51527

*NOTE- NET SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.1.2.2 (Con't)

ALUMINUM		2014		K(I C)		CRACK LENGTH		GROSS STRESS		K(I APP) STAN		K(I C) STAN							
CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST SPEC TEMP OR (F)	YIELD STR (KSI)	---SPECIMEN---		INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(I APP) (KBI*SQRT IN)	MEAN DEV	K(I C) (KBI*SQRT IN)	MEAN DEV	DATE	REFER			
					WIDTH (IN)	THICK B											2A(I) 2A(F)	S(I) S(MAX)	
T6	S	0.06	-320	T-L	69.3	4.000	0.062	1.230	---	39.30	52.14	---	---	---	---	---	1963 51527		
					69.3	4.000	0.063	1.230	---	30.30	44.75	---	---	---	---	---	---	---	1963 51527
					69.3	4.000	0.063	1.240	1.740	35.90	53.03	---	---	---	---	67.40*	---	---	1963 51527
					69.3	4.000	0.063	1.240	1.800	36.30	53.89	---	---	---	---	70.00*	---	---	1963 51527
					69.3	4.000	0.063	1.230	1.860	36.70	54.21	---	---	51.6/	3.9	72.68*	---	---	1963 51527
T6	S	0.06	R.T.	T-L	64.3	2.000	0.065	0.624	0.790	---	36.90	38.89*	---	---	43.37*	---	1973 86213		
					64.3	2.000	0.064	0.625	0.930	36.30	38.26*	---	---	---	---	30.83*	---	1973 86213	
					64.3	2.000	0.065	0.623	0.850	37.60	39.55*	---	---	---	---	49.03*	---	1973 86213	
					64.3	2.000	0.064	0.623	0.910	36.20	38.16*	---	---	---	---	49.80*	---	1973 86213	
					64.3	2.000	0.065	0.623	0.900	37.40	39.34*	---	---	---	---	50.99*	---	1973 86213	
					65.6	2.000	0.065	0.623	0.830	37.50	39.45*	---	---	---	---	48.02*	---	1973 86213	
T6	S	0.06	R.T.	T-L	65.6	2.000	0.067	0.625	0.760	---	35.60	37.52	---	---	42.77*	---	1973 86213		
					65.6	2.000	0.064	0.621	0.820	37.00	38.84*	---	---	---	---	46.76*	---	1973 86213	
					65.6	2.000	0.067	0.625	0.860	35.10	37.00	---	---	37.3/	0.4	46.18*	---	---	1973 86213
					63.2	3.970	0.063	1.230	1.620	---	34.20	50.56	---	---	---	---	60.94*	---	1963 51527
					63.2	3.970	0.063	1.240	1.480	---	33.60	49.93	---	---	---	---	56.12*	---	1963 51527
					63.2	3.970	0.063	1.240	1.690	---	32.80	48.74	---	---	---	---	59.25*	---	1963 51527
T6	S	0.06	R.T.	T-L	63.2	3.980	0.063	1.230	1.680	---	33.80	49.76	---	---	61.85*	---	1963 51527		
					63.2	3.980	0.063	1.240	1.690	---	30.70	45.61	---	---	49.0/	2.0	55.42*	---	1963 51527
					65.4	15.810	0.063	3.000	3.950	---	24.10	53.91	---	---	---	---	58.75	---	1973 86213
					65.4	15.810	0.064	4.000	4.830	---	20.40	53.25	---	---	---	---	59.66	---	1973 86213
					65.4	15.820	0.064	1.020	1.620	---	38.40	48.73	---	---	---	---	61.66	---	1973 86213
					65.4	15.820	0.064	6.010	6.860	---	14.60	49.32	---	---	---	---	54.38	---	1973 86213
T6	S	0.12	R.T.	T-L	62.2	3.000	0.126	1.130	1.620	---	29.40	42.99	---	---	57.67*	---	1973 86213		
					62.2	3.000	0.126	1.110	1.980	---	29.50	42.61	---	---	42.8/	0.3	56.49*	---	1973 86213
T6	P	0.25	R.T.	T-L	62.8	3.000	0.247	1.130	1.990	---	24.60	35.97	---	---	47.39*	---	1973 86213		
					62.8	3.000	0.247	1.160	1.640	---	24.00	35.75	---	---	35.9/	0.2	47.65*	---	1973 86213

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.1.2.2 (Con't)

ALUMINUM		2014		K(C)		CRACK LENGTH CROSS STRESS														
CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	--SPECIMEN--				K(APP)				K(C)		STAN DEV	DATE	REFER			
					WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	DNBET (KSI)	MAX (KSI)	MEAN (KSI)	DEV (KSI)	MEAN (KSI)	DEV (KSI)				MEAN (KSI)	DEV (KSI)	
T651	P	0.25	R. T.	L-T	62.2	4.000	0.249	1.330	2.120	---	32.80	50.92	72.96*	---	---	---	---	1973 86213		
					62.2	4.000	0.248	1.400	2.310	---	32.00	51.39	77.66*	---	---	---	---	---	1973 86213	
					64.3	4.000	0.252	1.400	2.380	---	32.10	51.55	80.52*	---	---	---	---	---	1973 86213	
					64.3	4.000	0.251	1.330	2.260	---	33.90	52.63	80.38*	---	---	---	---	---	1973 86213	
T651	P	0.25	R. T.	L-T	64.3	4.000	0.252	1.330	2.140	---	33.50	52.01	51.7/ 0.6	75.20*	---	---	---	1973 86213		
					66.4	20.000	1.000	6.750	9.950	---	14.50	51.82	68.04	---	---	---	---	---	1973 86213	
					60.7	4.000	0.250	1.420	2.110	---	26.20	42.48	58.02*	---	---	---	---	---	---	1973 86213
					62.2	4.000	0.252	1.330	1.840	---	27.20	42.23	56.32*	---	---	---	---	---	---	1973 86213
T651	P	0.25	R. T.	T-L	62.2	4.000	0.252	1.330	1.840	---	27.10	42.07	53.20*	---	---	---	---	1973 86213		
					62.2	4.000	0.252	1.410	2.140	---	25.90	41.79	58.14*	---	---	---	---	---	1973 86213	
					62.2	4.000	0.252	1.330	1.900	---	27.20	42.23	42.2/ 0.3	54.84*	---	---	---	---	---	1973 86213
					65.8	20.000	1.000	6.940	9.370	---	9.10	32.49	40.55	---	---	---	---	---	---	1973 86213

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.1.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2014			
CONDITION: T6					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.05	R=+0.25	R=+0.40	
DELTA K MIN	A: 5.69	.79			
	B: 5.86		2.14		
	C: 4.82			1.16	
	D:				
	5.00			1.37	
	6.00	1.06	2.27	2.74	
	7.00	2.11	3.39	4.39	
	8.00	3.38	4.90	6.46	
	9.00	4.80	6.91	9.30	
	10.00	6.41	9.59	13.5	
	13.00	13.6	24.0		
DELTA K MAX	A: 13.77	16.4			
	B: 14.47		36.6		
	C: 11.62			26.0	
	D:				
ROOT MEAN SQUARE		8.62	9.37	5.28	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8	1			
	0.8-1.25	5	4	4	
	1.25-2.0				
	>2.0				

CONDITION/HT: T6
 FORM: 0.04- 0.06" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 2.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 67.0 KSI
 ULT STRENGTH: 74.0 KSI
 SPECIMEN THK: 0.040- 0.064"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 86734

ALUM.
 ALLOY

2014

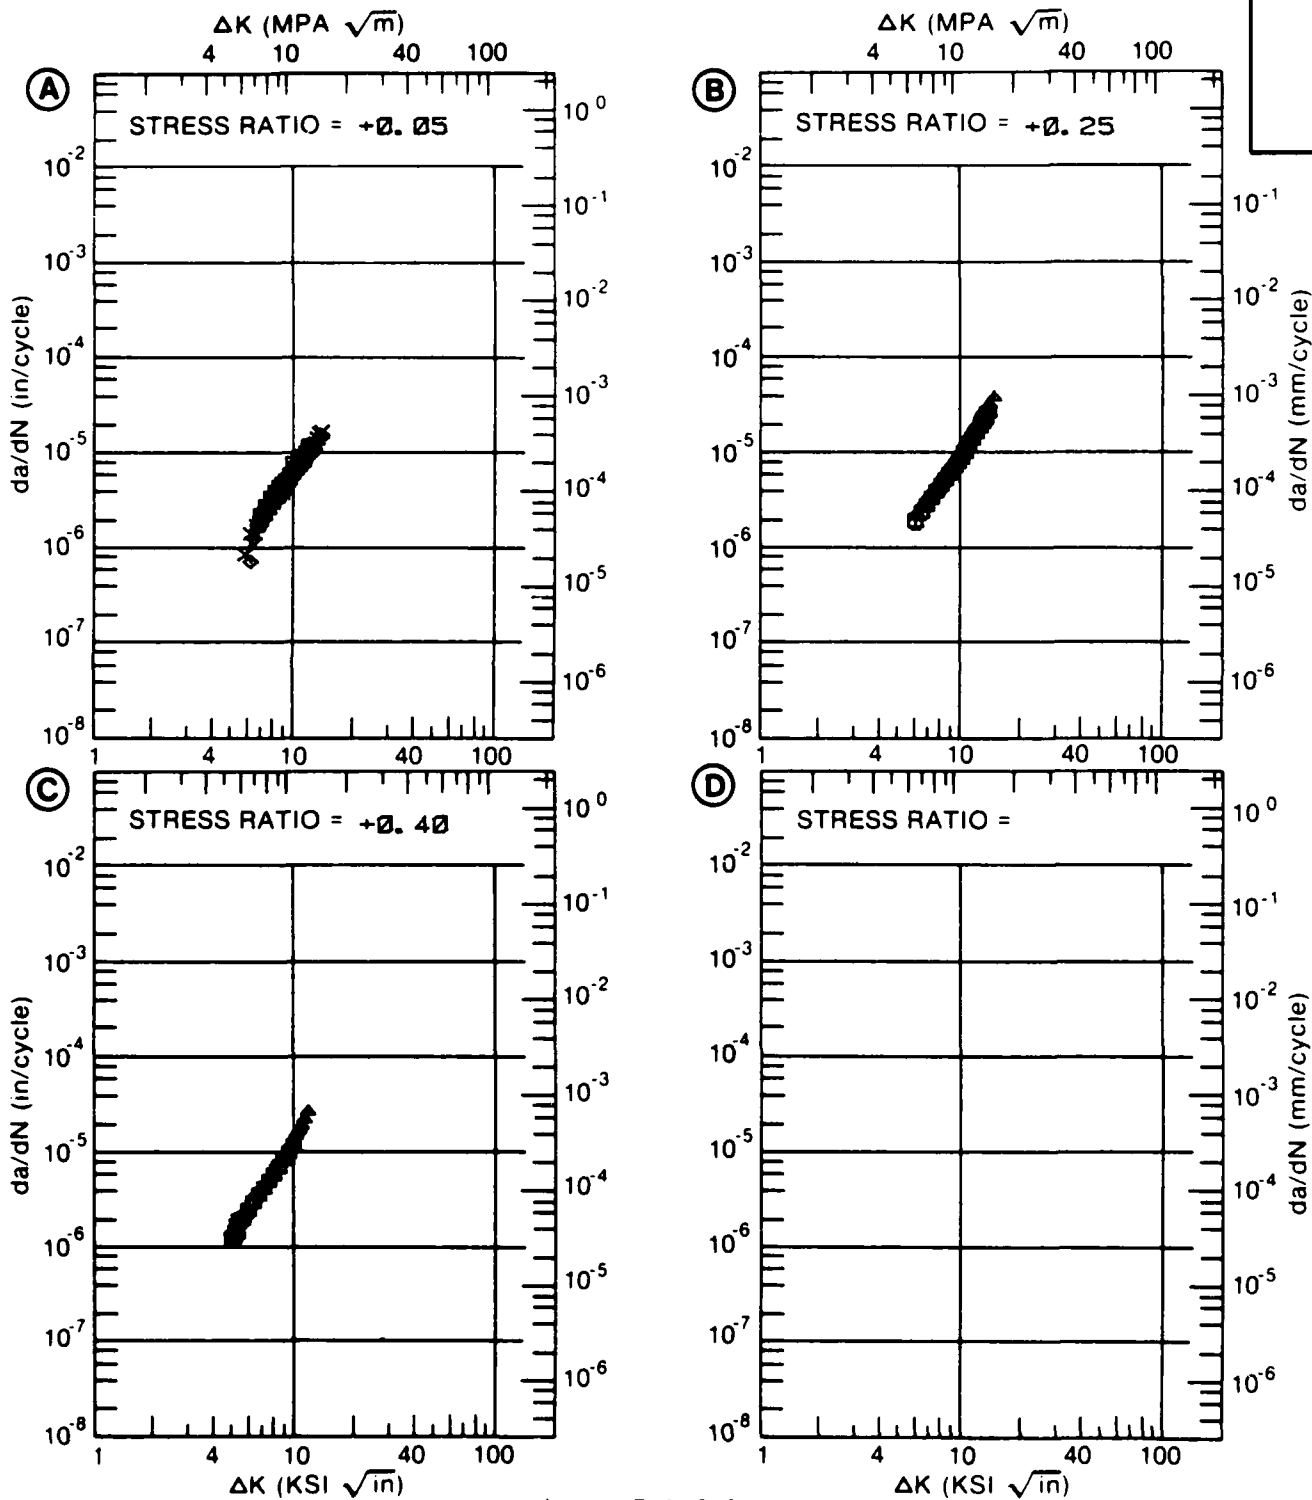


Figure 7.1.3.1

TABLE 7.1.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2014	
CONDITION: T6			
ENVIRONMENT: R. T., LAB AIR			
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)	
		A	B
		R=+0.50	R=+0.57
DELTA K MIN	A: 4.13	.667	
	B: 4.14		.435
	C:		
	D:		
	5.00	1.57	1.02
	6.00	2.88	2.01
	7.00	4.58	3.34
	8.00	7.15	
DELTA K MAX	A: 8.87	10.8	
	B: 7.73		4.59
	C:		
	D:		
ROOT MEAN SQUARE PERCENT ERROR		6.27	6.15
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	4	1 1

CONDITION/HT: T6
 FORM: 0.04- 0.06" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 2.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 67.0 KSI
 ULT. STRENGTH: 74.0 KSI
 SPECIMEN THK: 0.040- 0.063"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 96734

ALUM.
 ALLOY

2014

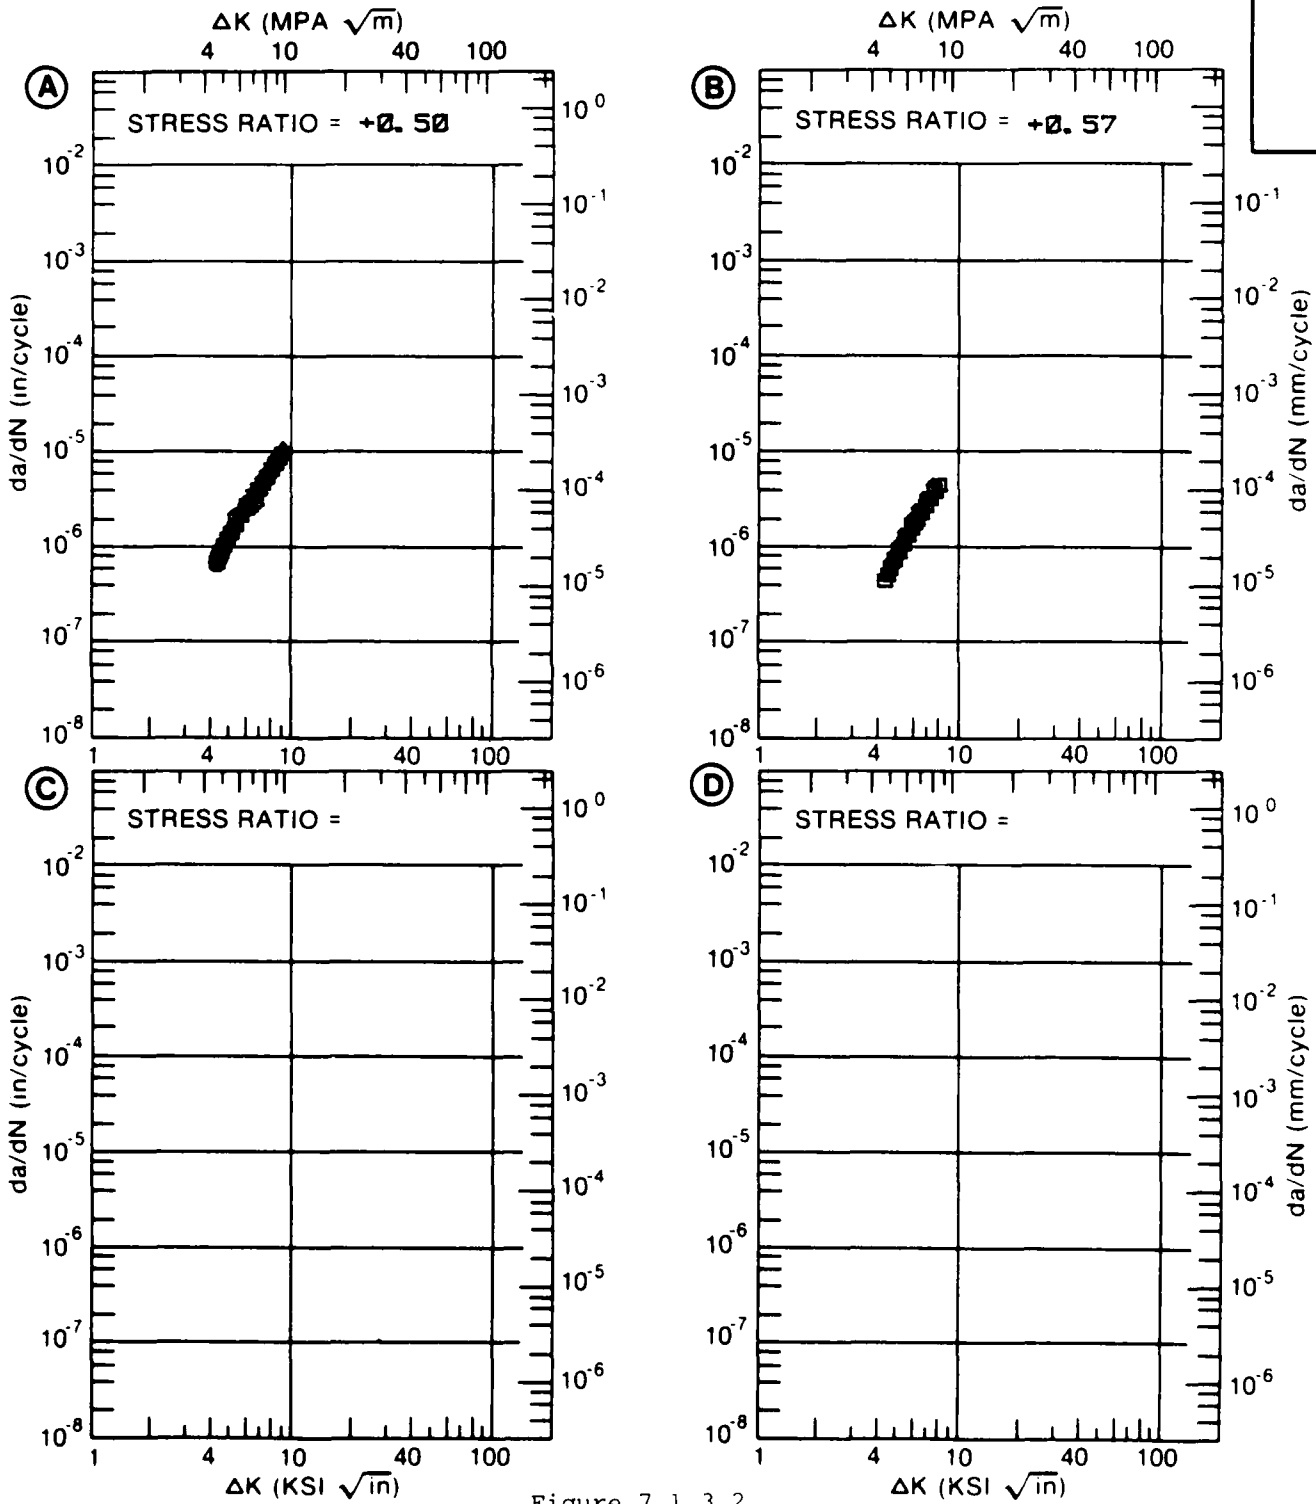


Figure 7.1.3.2

TABLE 7.1.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2014			
CONDITION: T6					
ENVIRONMENT: R. T., LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.05	R=+0.25	R=+0.40	
A:	5.65	1.11			
DELTA K B:	5.54		1.61		
MIN C:	4.88			1.14	
D:					
	5.00			1.29	
	6.00	1.39	2.10	2.70	
	7.00	2.33	3.42	4.40	
	8.00	3.50	5.18	6.66	
	9.00	5.00	7.60	10.2	
	10.00	7.03	11.0	16.3	
	13.00	19.8			
A:	13.51	23.9			
DELTA K B:	12.91		33.1		
MAX C:	11.48			36.6	
D:					
ROOT MEAN SQUARE		12.89	12.95	13.84	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25	3	4	4	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T6
 FORM: 0.04- 0.06" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 2.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 67.0 KSI
 ULT. STRENGTH: 74.0 KSI
 SPECIMEN THK: 0.040- 0.063"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 86734

ALUM.
ALLOY

2014

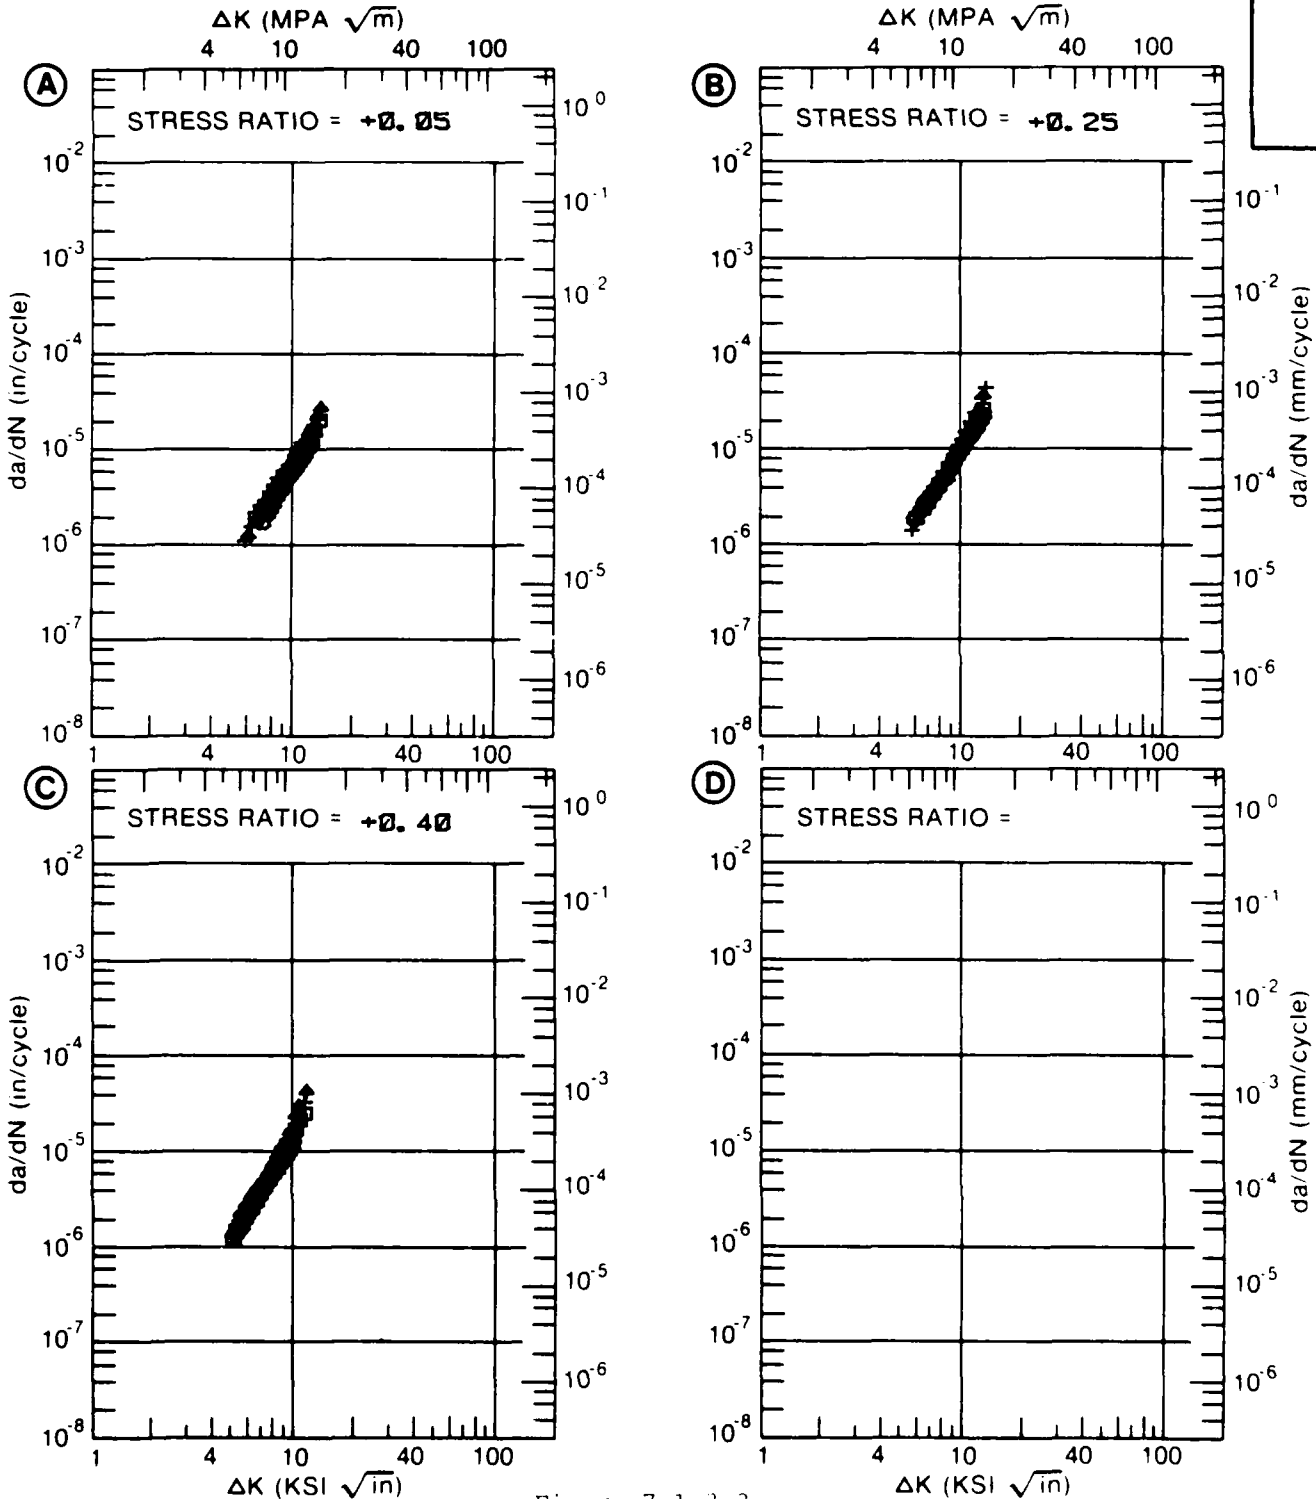


Figure 7.1.3.3

TABLE 7.1.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2014			
CONDITION: T6					
ENVIRONMENT: R. T., LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.50	R=+0.57		
DELTA K A:	4.17	.731			
DELTA K B:	3.66		.345		
MIN C:					
D:					
	4.00		.497		
	5.00	1.59	1.25		
	6.00	3.10	2.56		
	7.00	5.36	4.39		
	8.00	8.87			
DELTA K A:	8.66	12.3			
DELTA K B:	7.88		6.28		
MAX C:					
D:					
ROOT MEAN SQUARE		11.45	16.08		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25	3	4		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T6
 FORM: 0.04- 0.06" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 2.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 67.0 KSI
 ULT. STRENGTH: 74.0 KSI
 SPECIMEN THK: 0.040- 0.063"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 86734

ALUM.
 ALLOY

2014

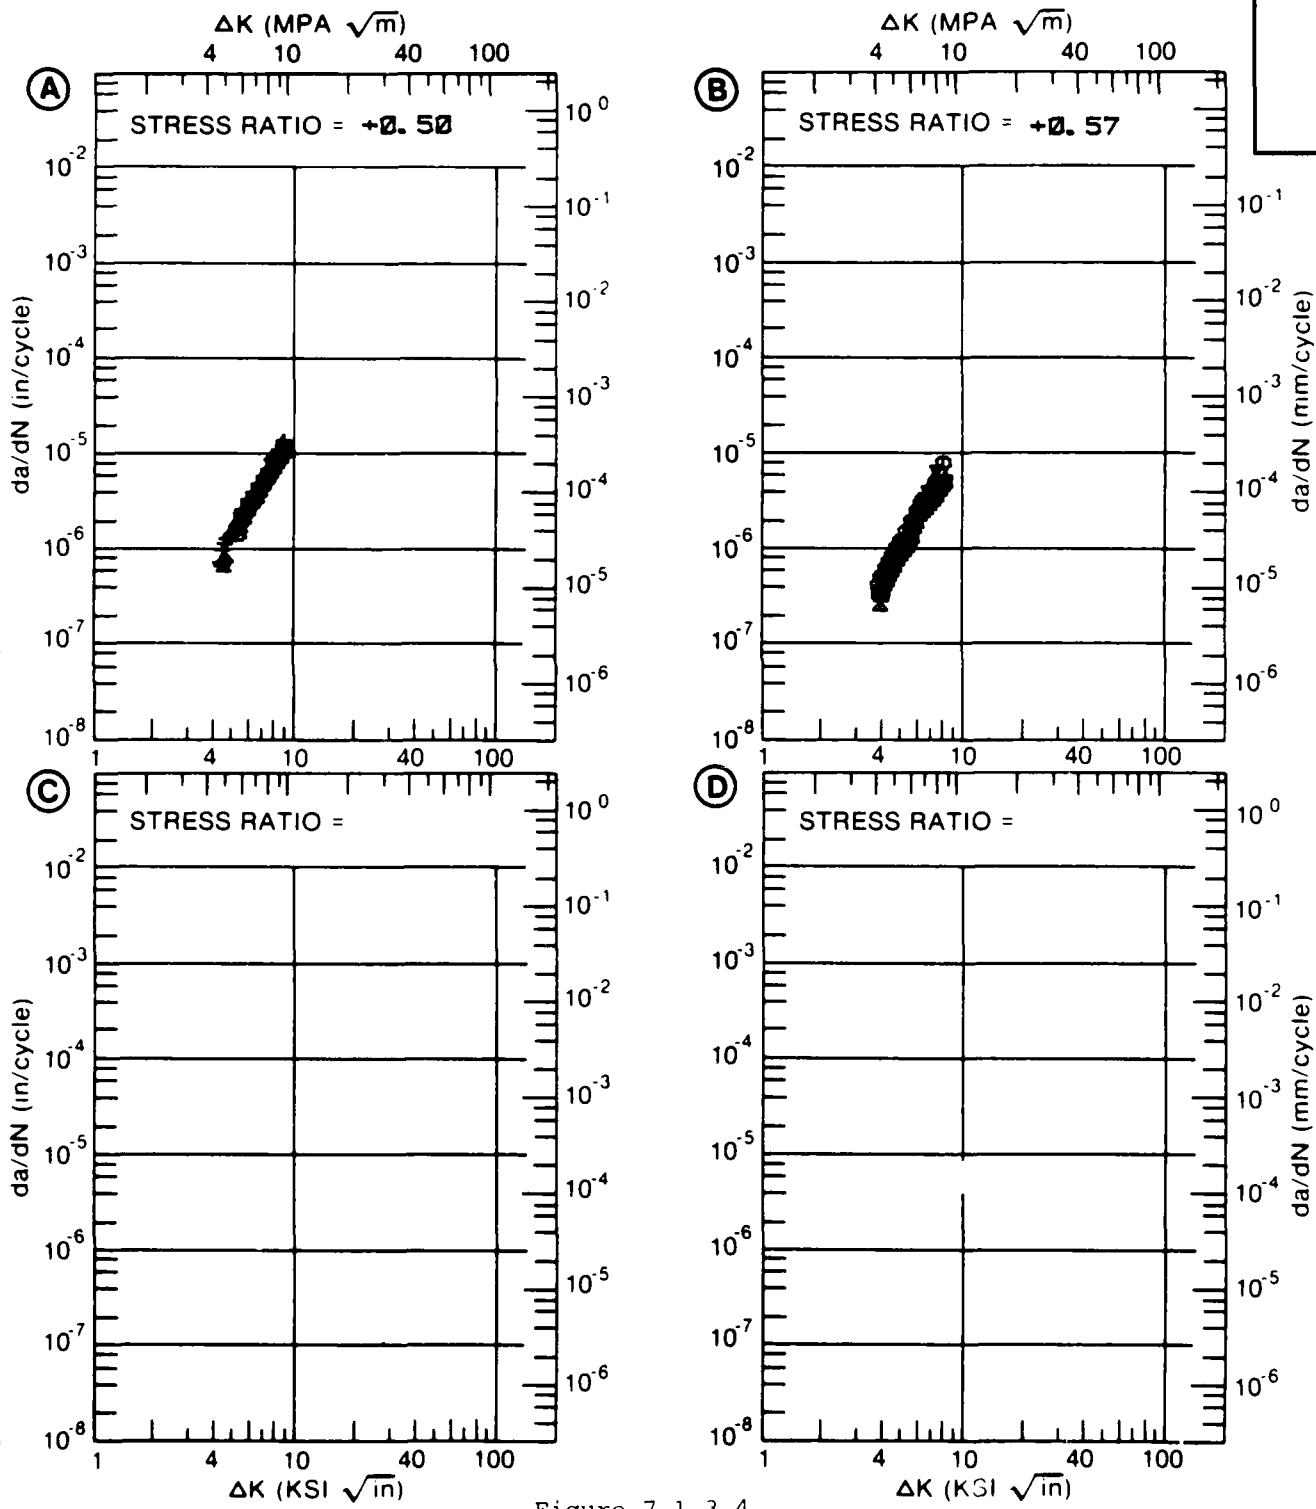


Figure 7.1.3.4

TABLE 7.1.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.5 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 2014
CONDITION: T6

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. H. H. A.		
DELTA K MIN	A: 6.53	.315			
	B: 4.08		.543		
	C:				
	D:				
	5.00		1.20		
	6.00		2.41		
	7.00	.479	4.42		
	8.00	.885	7.73		
	9.00	1.35	13.2		
	10.00	1.93	22.0		
	13.00	7.89	97.4		
DELTA K MAX	A: 15.67	60.8			
	B: 15.39		309.		
	C:				
	D:				

ROOT MEAN SQUARE 18.38 21.24
PERCENT ERROR

LIFE PREDICTION RATIO SUMMARY (NP/NA)
0.0-0.5
0.5-0.8
0.8-1.25
1.25-2.0
>2.0

CONDITION/HT: T6
 FORM: FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.05
 FREQUENCY:

YIELD STRENGTH: 64.1 KSI
 ULT. STRENGTH: 68.2 KSI
 SPECIMEN THK: 0.400"
 SPECIMEN WIDTH: 2.000- 4.000"
 REFERENCES: BW001

ALUM.
 ALLOY

2014

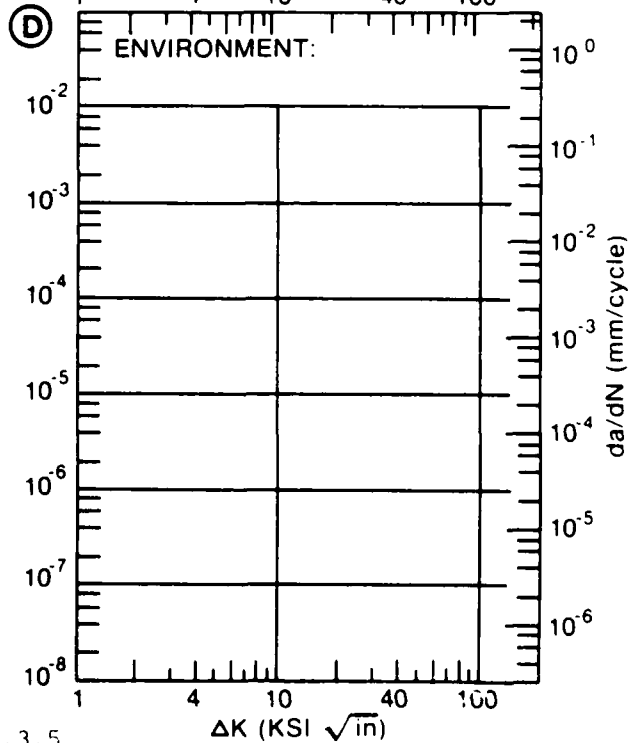
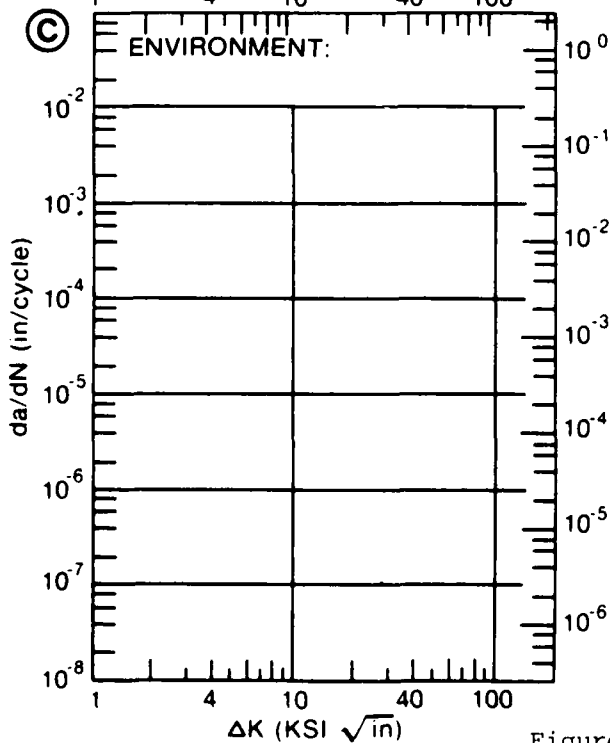
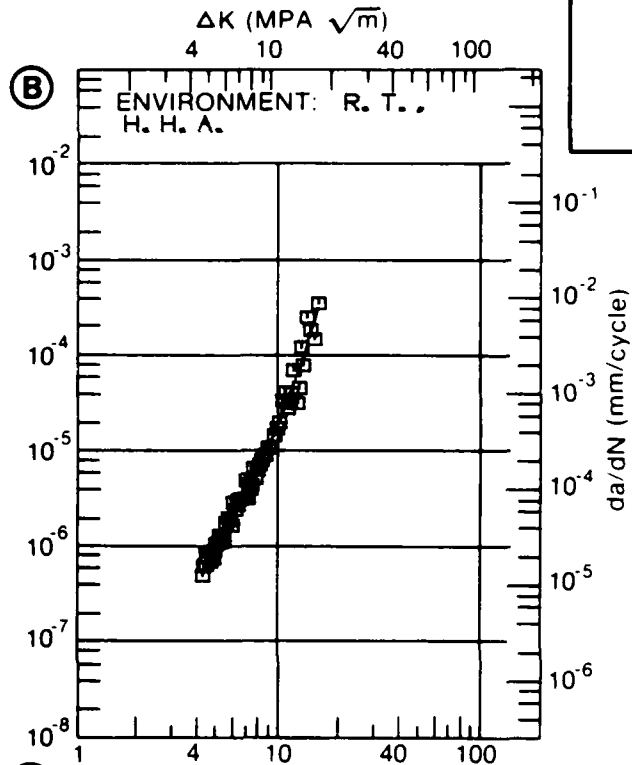
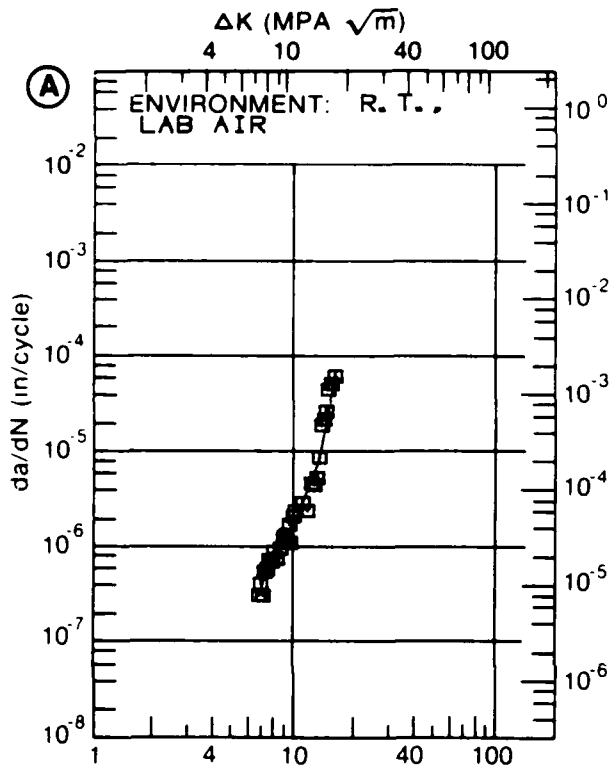


Figure 7.1.3.5

TABLE 7.1.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.6 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2014
CONDITION: T6
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=-1.00			
DELTA K A:	4.85	.662			
MIN B:					
C:					
D:					
	5.00	.783			
	6.00	1.88			
	7.00	3.42			
	8.00	5.26			
	9.00	7.31			
	10.00	9.51			
	13.00	17.1			
	16.00	27.3			
	20.00	48.8			
DELTA K A:	21.09	57.2			
MAX B:					
C:					
D:					

ROOT MEAN SQUARE 8.35
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T6
 FORM: 5.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 9.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.400"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: BW001

ALUM.
ALLOY

2014




Figure 7.1.3.6

TABLE 7.1.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.7 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2014			
CONDITION: T6					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-1.00			
DELTA K	A: 4.79	1.01			
MIN	B:				
	C:				
	D:				
	5.00	1.26			
	6.00	2.86			
	7.00	5.18			
	8.00	8.23			
	9.00	12.1			
	10.00	17.4			
	13.00	58.2			
	16.00	224.			
DELTA K	A: 17.10	284.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		26.13			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T6
 FORM: 5.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 9.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 64.1 KSI
 ULT. STRENGTH: 68.2 KSI
 SPECIMEN THK: 0.400"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: BW001

ALUM.
ALLOY

2014

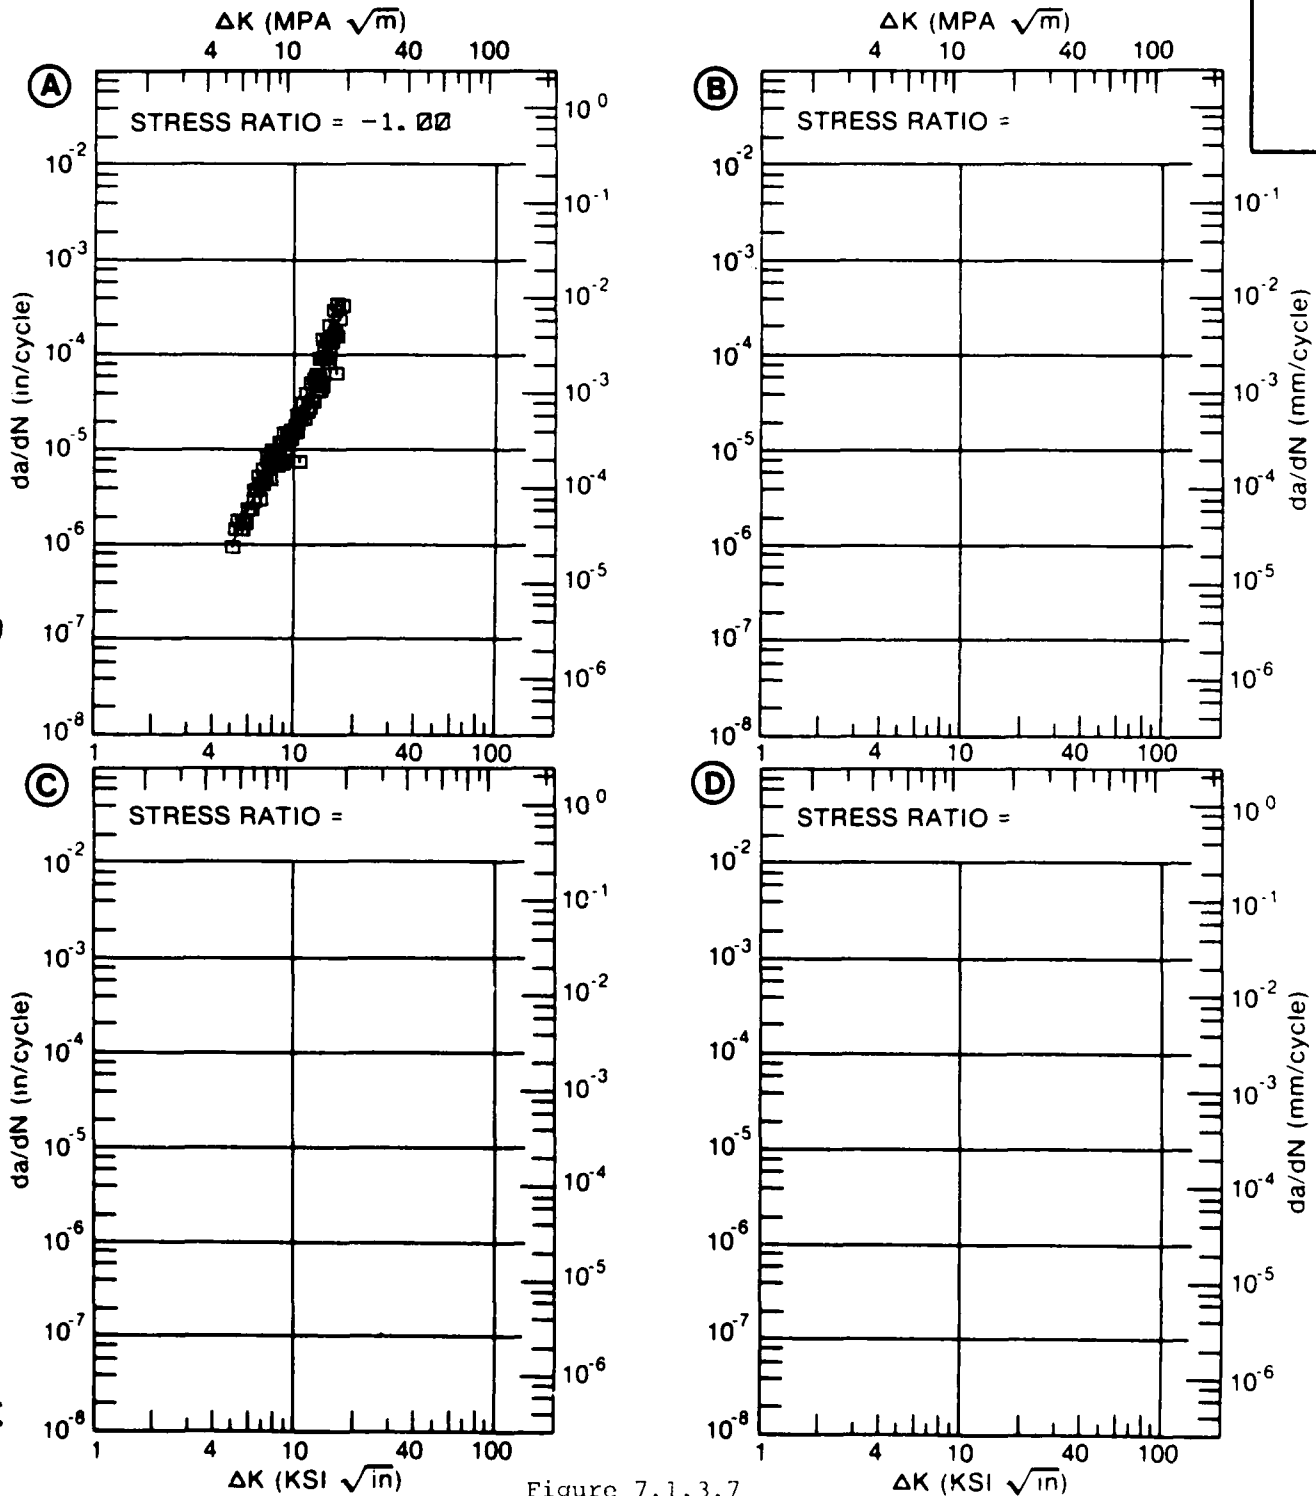


Figure 7.1.3.7

TABLE 7.1.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2014			
CONDITION: T6					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 24.55	196.			
MIN	B:				
	C:				
	D:				
	25.00	236.			
	30.00	549.			
	35.00	1271.			
	40.00	1575.			
DELTA K	A: 46.11	2655.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		28.37			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	4			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T6
 FORM: 1.00" TH ROLLED BAR
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.00
 FREQUENCY: 5.20 HZ

YIELD STRENGTH: 60.2- 60.5 KSI
 ULT. STRENGTH: 66.0- 67.3 KSI
 SPECIMEN THK: 0.253- 0.260"
 SPECIMEN WIDTH: 7.500- 7.517"
 REFERENCES: 86213

ALUM. ALLOY
2014

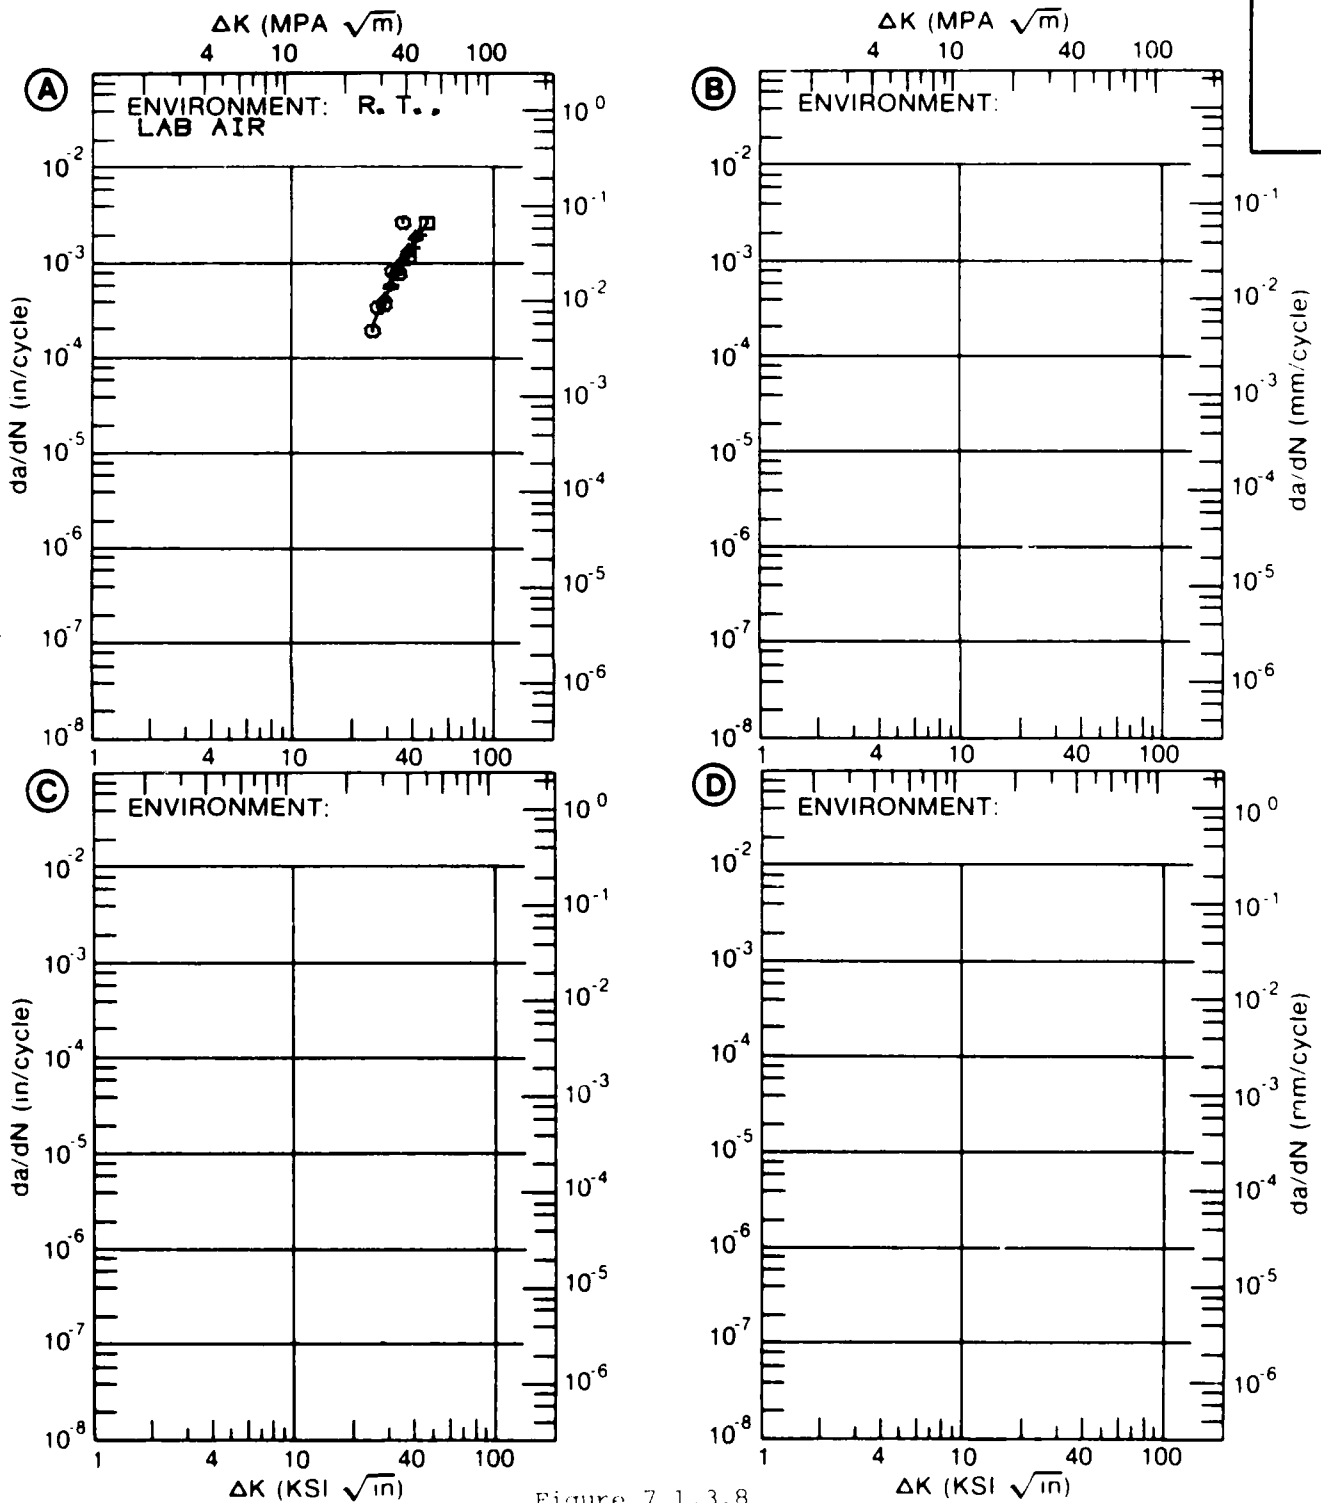


Figure 7.1.3.8

TABLE 7.1.3.10

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2014			
CONDITION: T451					
K MAX (KSI*IN**1/2)		DA/DT (10**-6 IN/HOUR)			
		A	B	C	D
		E= F			
		3X/DAY-3.5NACL			
K MAX	A:				
MIN	B:				
	C:				
	D:				
		200.00			
K MAX	A:				
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		0.00			
PERCENT ERROR					

CONDITION/HT: T451
 FORM: 1.5" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: S-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 78313

ALUM. ALLOY
2014

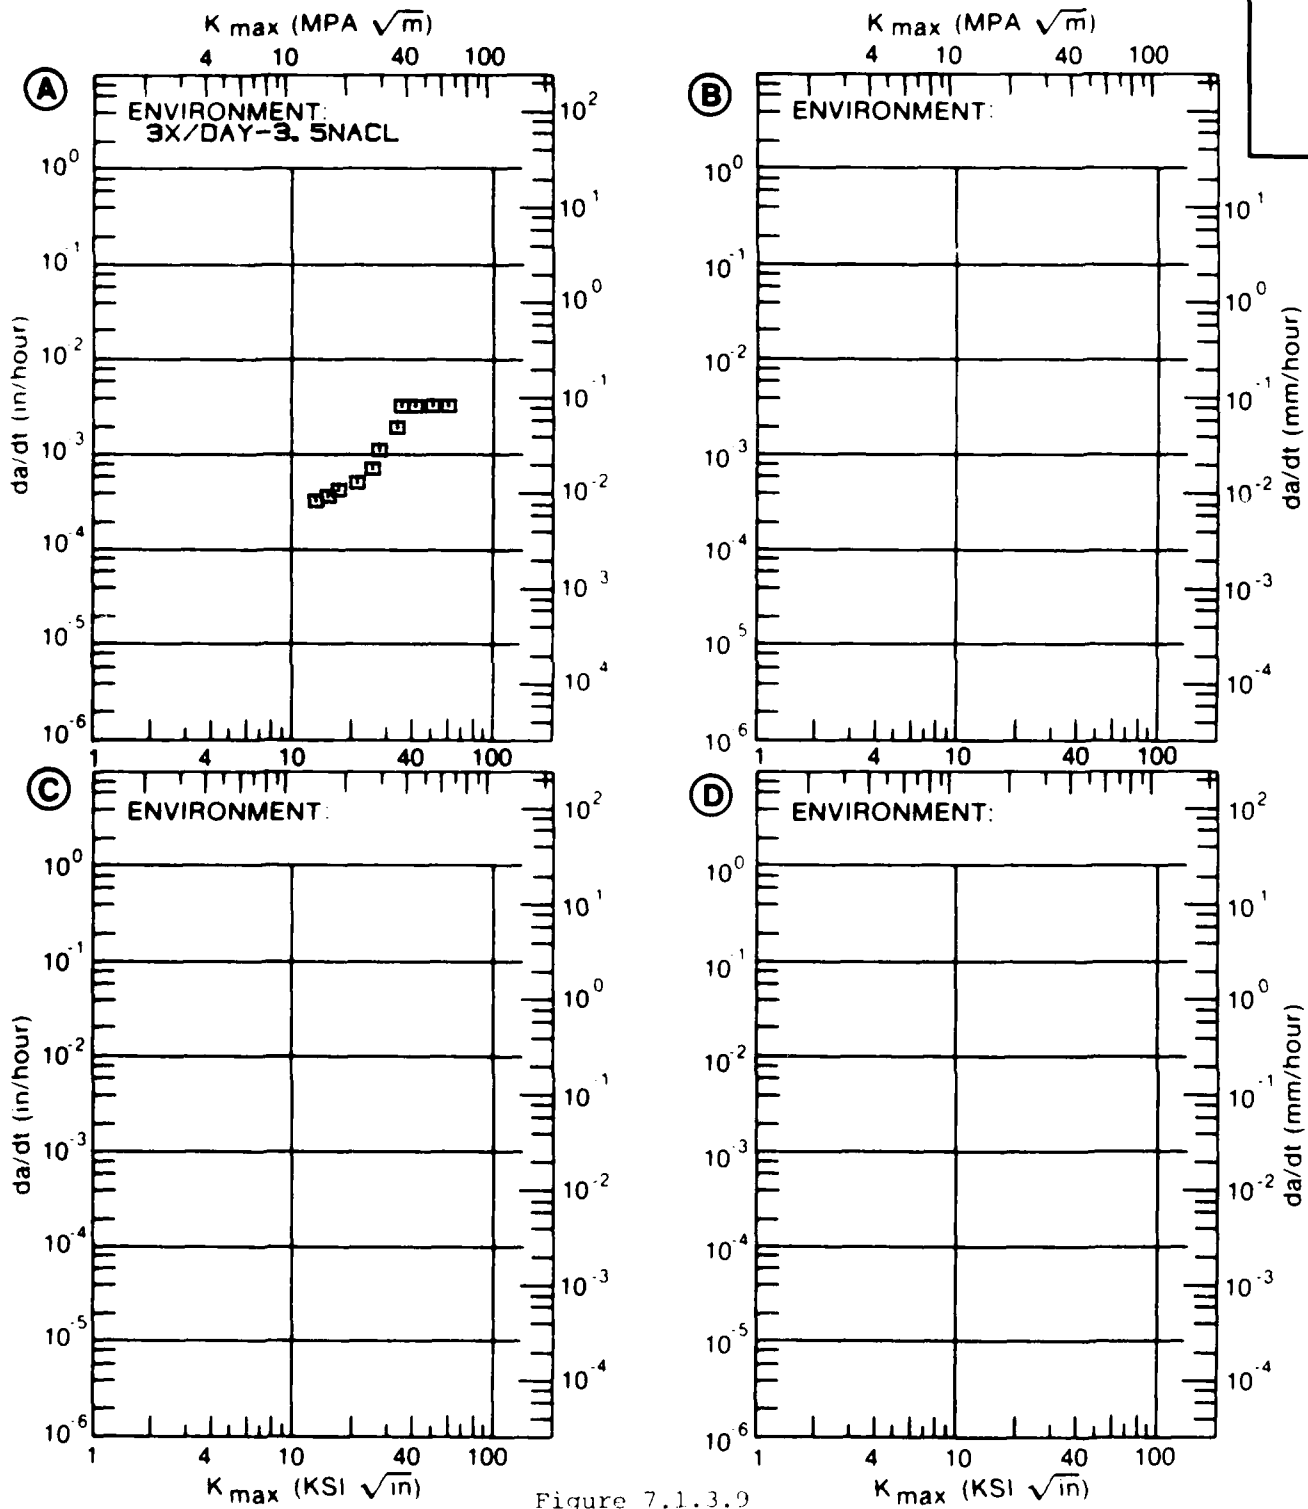


Figure 7.1.3.9

TABLE 7.1.3.9

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.1.3.9 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 2014
CONDITION: T651

K MAX
(KSI*IN**1/2)

DA/DT (10**-6 IN/HOUR)

A

B

C

D

E= F

3X/DAY-3.5NACL

K MAX A:
MIN B:
C:
D:

200.00

K MAX A:
MAX B:
C:
D:

ROOT MEAN SQUARE
PERCENT ERROR

0.00

CONDITION/HT: T651
 FORM: 2.0" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: S-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 78313

ALUM.
ALLOY

2014

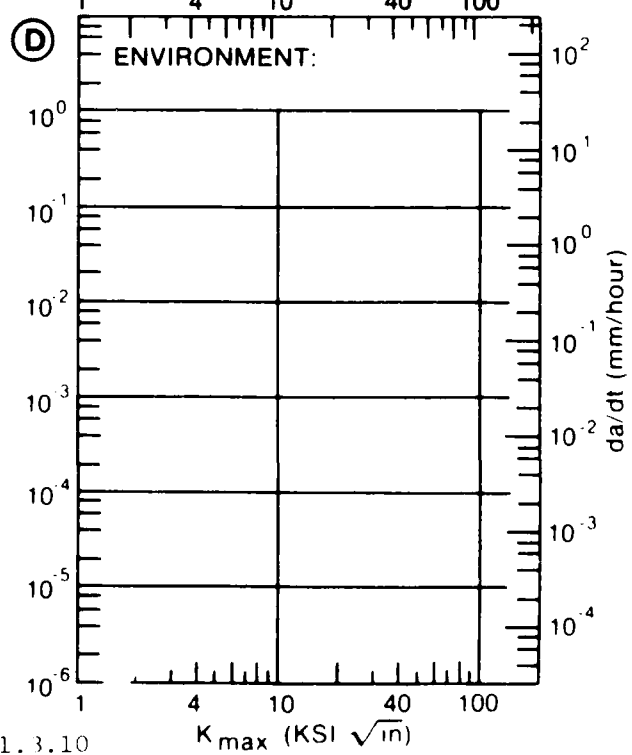
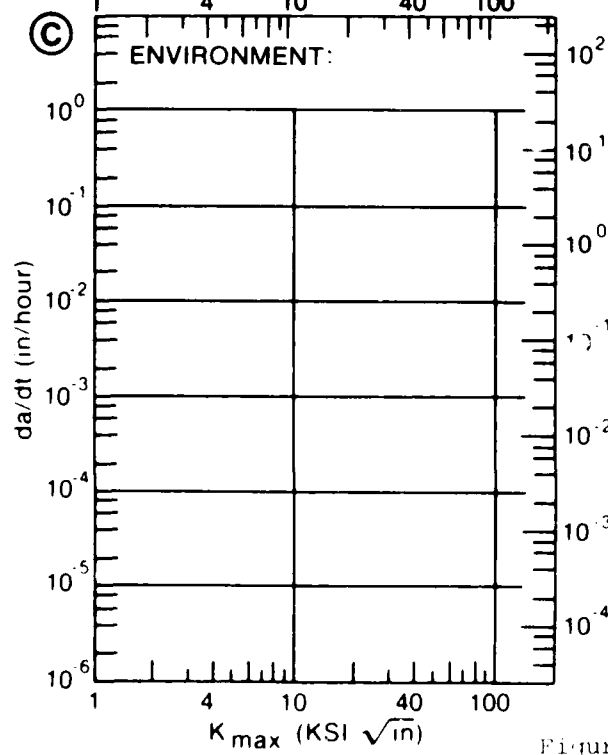
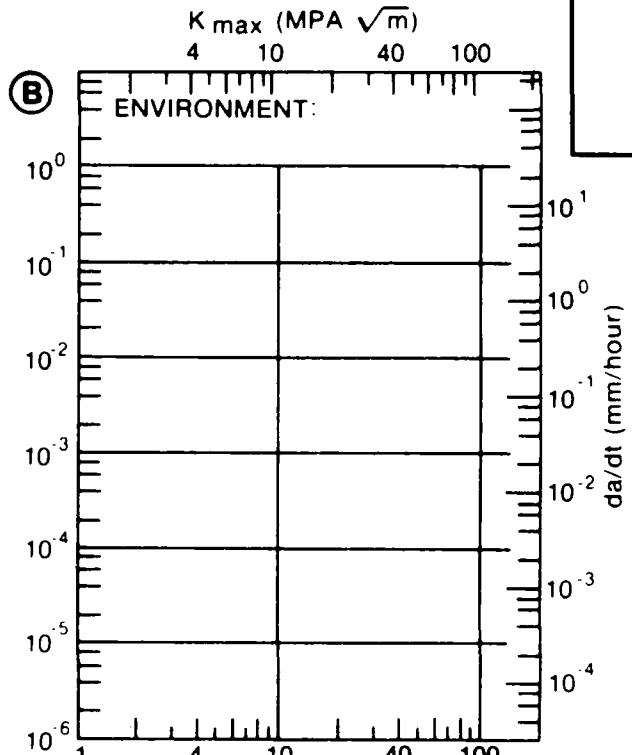
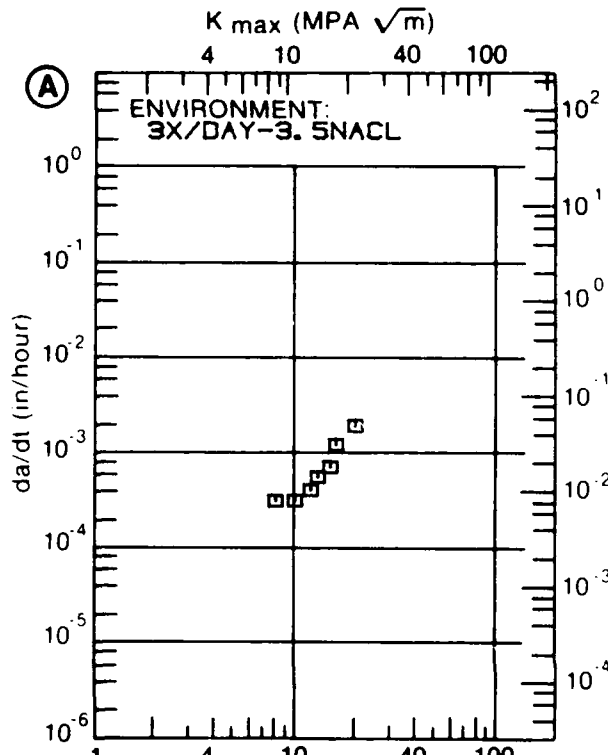


Figure 7.1.3.10

TABLE 7.1.3.11

CONDITION	ALUMINUM		TEST SPEC YIELD STR (KSI)	ENVIRONMENT	PRODUCT-- FORM THICK (IN)	TEMP OR (F)	S-L	W	SPECIMEN--		CRACK LENGTH (IN)	K (ISCC)	K (ISCC) MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	WIDTH (IN)	THICK (IN)							DESIGN (**SG)	A						
T6	F	8.00	R. T.	61.0 SYNTH SEAWATER	2.000	1.000	CANT	19.00	16.00						1972	82675
T651	P	2.50	R. T.	8-L INDUSTRIAL ATM	2.000	1.000	CT	18.70	7.00						1973	86688
T651	P	2.50	R. T.	8-L SALT-DICHRD-MATE-ACETATE	2.000	1.000	CT	18.70	7.00						1973	86688
T651	P	2.50	R. T.	8-L SEACOAST ATM	2.000	1.000	CT	18.70	7.00						1973	86688

TABLE 7.2.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 2020 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION		(NUMBER OF SPECIMENS)	
	I-II	I-L	I-L	S-L
T651	23.0 ± 2.4 (8)	17.2 ± 0.3 (4)		

TABLE 7.2.1.1.2
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 ALUMINUM 2024

TEST CONDITIONS		ENVIRONMENT	LAB AIR AT R T	FATIGUE CRACK GROWTH RATES					
SPECIMEN ORIENTATION (L-T)	PRODUCT FORM			STRESS RATIO	FREQ (HZ)	DELTA K LEVEL (KSI SQRT(IN))	(MICRO IN/CYCLE)		
	SHEET	0.00	1000	2.5	5	10	20	50	100
	PLATE	0.50	500						100
	PLATE	0.60	500						100

TABLE 7.2.2.1

CONDITION	ALUMINUM				2020		K(1C)		K(1C) STAN K(1C) MEAN DEV (KSI*SQRT IN)	DATE	REFER	
	--PRODUCT-- FORM	THICK (IN)	TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	---SPECIMEN---		CRACK LENGTH (IN)	2.5* K(1C)/TVS) (IN)				
					WIDTH (IN)	THICK (IN)						DESIGN
T6	P	0.78	86	L-T	75.5	1.500	0.751	CT	0.745	0.18	20.50	1973 86213
		0.78			75.5	1.500	0.752	CT	0.728	0.17	19.90	1973 86213
		0.78			75.5	1.500	0.752	CT	0.697	0.18	20.00	1973 86213
T6	E	0.69	R.T.	L-T	75.5	1.500	0.652	NB	0.747	0.22	22.40	1973 86213
T651	P	1.37	R.T.	L-T	76.3	3.000	1.376	NB	1.413	0.17	19.70	1973 86213
		1.37			77.0	3.000	1.385	NB	1.390	0.18	20.90	1973 86213
		1.37			77.5	3.000	1.375	NB	1.460	0.24	23.80	1973 86213
		1.37			77.5	2.000	0.999	CT	0.967	0.22	22.90	1973 86213
		1.37			77.5	3.000	1.375	NB	1.400	0.31	27.20	1973 86213
		1.37			77.5	3.000	1.375	NB	1.450	0.23	23.60	1973 86213
		1.37			77.5	3.000	1.375	NB	1.420	0.26	24.80	1973 86213
		1.37			77.5	2.000	0.999	CT	1.007	0.19	21.10	1973 86213
T651	P	1.37	84	L-T	76.3	2.000	1.000	CT	0.963	0.18	20.30	1973 86213
		1.37			76.3	2.000	1.000	CT	0.943	0.22	22.80	1973 86213
		1.37			76.3	2.000	1.001	CT	0.950	0.18	20.50	1973 86213
T651	P	1.37	R.T.	T-L	77.4	3.000	1.379	NB	1.526	0.12	17.00	1973 86213
		1.37			77.5	3.000	1.378	NB	1.560	0.12	16.80	1973 86213
		1.37			78.4	2.000	0.999	CT	1.024	0.12	17.50	1973 86213
		1.37			78.4	1.990	0.999	CT	0.964	0.12	17.40	1973 86213
T651	P	1.37	84	T-L	77.4	2.000	1.002	CT	1.019	0.13	17.00	1973 86213
		1.37			77.4	2.000	1.002	CT	1.020	0.13	17.80	1973 86213
		1.37			77.4	2.000	1.001	CT	1.021	0.12	17.10	1973 86213
T651	P	1.37	88	S-L	74.4	0.990	0.500	CT	0.506	0.11	15.30	1973 86213
		1.37			74.4	1.000	0.500	CT	0.508	0.11	15.50	1973 86213

TABLE 7.2.2.2

ALUMINUM		2020		K(C)		CRACK LENGTH CROSS STRESS													
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	---SPECIMEN---		INIT		FINAL		ONSET		MAX		K(APP)		K(C)		K(C) STAN	
				WIDTH (IN)	THICK (IN)	(IN)	(IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI*SQRT IN)	(KSI*SQRT IN)	MEAN DEV	MEAN DEV	MEAN DEV	DATE REFER		
				W	B	2A(O)	2A(F)	S(O)	S(MAX)										
BUCKLING OF CRACK EDGES NOT RESTRAINED																			
T6	S	0.06	R.T.	L-T	75.9	2.000	0.062	0.622	0.890	---	30.80	32.40	---	41.62	---	---	---	---	1973 86213
		0.06			75.9	2.000	0.062	0.622	0.760	---	29.60	31.14	---	35.36	---	---	---	---	1973 86213
		0.06			75.9	2.000	0.062	0.621	0.890	---	30.40	31.91	---	41.08	---	---	---	---	1973 86213
		0.06			77.0	2.000	0.064	0.625	0.650	---	24.40	25.72	---	26.39	---	---	---	---	1973 86213
		0.06			77.0	2.000	0.064	0.625	0.680	---	25.50	26.88	---	28.41	---	34.6/	7.0	---	1973 86213
T6	S	0.06	R.T.	L-T	75.9	3.000	0.061	1.070	1.140	---	21.10	29.72	---	31.05	---	---	---	---	1973 86213
		0.06			75.9	3.000	0.062	1.100	1.140	---	19.90	28.56	---	29.28	---	30.2/	1.3	---	1973 86213
T6	S	0.06	R.T.	L-T	76.9	15.800	0.063	3.000	3.480	---	17.00	37.75	---	40.98	---	---	---	---	1973 86213
		0.06			76.9	15.810	0.063	6.010	6.010	---	10.20	34.46	---	34.46	---	---	---	---	1973 86213
		0.06			76.9	15.810	0.063	3.020	3.020	---	16.60	36.99	---	36.99	---	---	---	---	1973 86213
		0.06			76.9	15.820	0.063	1.020	1.020	---	27.80	35.28	---	36.9/	---	2.9	---	---	1973 86213
T6	S	0.06	R.T.	T-L	75.8	2.000	0.062	0.622	0.870	---	26.60	27.98	---	35.31	---	---	---	---	1973 86213
		0.06			75.8	2.000	0.062	0.622	0.880	---	27.20	28.61	---	36.43	---	---	---	---	1973 86213
		0.06			75.8	2.000	0.062	0.624	0.870	---	25.60	26.98	---	33.98	---	---	---	---	1973 86213
		0.06			76.0	2.000	0.064	0.625	0.660	---	21.70	22.87	---	23.71	---	---	---	---	1973 86213
		0.06			76.0	2.000	0.064	0.625	0.625	---	21.70	22.87	---	22.87	---	30.5/	6.6	---	1973 86213
T6	S	0.06	R.T.	T-L	75.8	3.000	0.061	1.190	1.240	---	17.40	26.40	---	27.21	---	---	---	---	1973 86213
		0.06			75.8	3.000	0.062	1.070	1.120	---	19.50	27.47	---	28.34	---	27.8/	0.8	---	1973 86213
T6	S	0.06	R.T.	T-L	75.6	15.810	0.063	6.000	6.000	---	9.30	31.39	---	31.39	---	---	---	---	1973 86213
		0.06			75.6	15.810	0.063	3.010	3.010	---	16.10	35.81	---	35.81	---	---	---	---	1973 86213
		0.06			75.6	15.820	0.063	1.020	1.020	---	28.00	35.53	---	35.53	---	---	---	---	1973 86213
		0.06			75.6	15.820	0.063	4.010	4.010	---	13.80	36.07	---	36.07	---	---	---	---	1973 86213
		0.06			75.6	15.820	0.063	6.000	6.000	---	10.00	33.74	---	33.74	---	34.5/	2.0	---	1973 86213
BUCKLING OF CRACK EDGES NOT RESTRAINED																			
T651	S	0.12	R.T.	L-T	76.1	3.000	0.127	1.060	1.310	---	25.50	35.69	---	41.58	---	---	---	---	1973 86213
		0.12			76.1	3.000	0.127	1.080	1.300	---	25.80	36.37	---	41.82	---	---	---	---	1973 86213
		0.12			76.1	3.000	0.127	1.070	1.400	---	27.30	38.45	---	46.96	---	---	---	---	1973 86213

TABLE 7.2.2.2 (Con't)

CONDITION	ALUMINUM		2020		K(C)		CRACK LENGTH CROSS STRESS										K(APP) STAN		K(C) STAN																										
	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	---SPECIMEN---		WIDTH (IN)	THICK (IN)	INIT		FINAL (IN)	DNSET (KSI)	MAX (KSI)	K (APP) (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	DEV	STAN	K (C) (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	DEV	DATE	REFER																								
				H	B			2A(D)	2A(F)													S(D)	S(MAX)																						
T651	S	0.12	R. T.	L-T	76.1	3.000	0.127	1.060	1.270	---	25.80	36.11	41.08	---	---	---	---	---	---	---	1973	86213																							
																							0.12	76.3	3.000	0.127	1.100	1.400	---	25.20	36.17	43.35	---	---	---	---	---	---	---	---	---	---	---		
																							0.12	76.3	3.000	0.127	1.070	1.260	---	24.20	34.09	38.30	---	---	---	---	---	---	---	---	---	---	---	---	
																							0.12	76.3	3.000	0.127	1.090	1.320	---	23.00	32.81	37.73	---	---	---	---	---	---	---	---	---	---	---	---	
																							0.12	76.3	3.000	0.127	1.060	1.320	---	27.40	38.35	44.95	---	---	---	---	---	---	---	---	---	---	---	---	
																							0.12	77.5	3.000	0.127	1.070	1.390	---	23.90	33.66	40.87	---	---	---	---	---	---	---	---	---	---	---	---	
																							0.12	77.5	3.000	0.127	1.060	1.270	---	24.30	34.01	38.69	---	---	---	---	---	---	---	---	---	---	---	---	
																							0.12	77.5	3.000	0.127	1.080	1.380	---	24.00	34.02	40.80	---	---	---	---	---	---	---	---	---	---	---	---	
																							0.12	77.5	3.000	0.127	1.070	1.360	---	23.80	33.52	39.98	---	---	---	---	---	---	---	---	---	---	---	---	
																							0.25	R. T.	L-T	77.4	3.000	0.256	1.200	1.490	---	14.50	22.13	26.31	---	---	---	---	---	---	---	---	---	---	
																							0.25	77.4	3.000	0.256	1.170	1.420	---	15.00	22.48	26.11	---	---	---	---	---	---	---	---	---	---	---		
																							0.25	77.4	3.000	0.255	1.000	1.310	---	16.40	22.09	22.2/ 0.2	26.74	---	---	---	---	---	---	---	---	---	---		
T651	P	0.25	R. T.	L-T	77.4	4.000	0.256	1.330	1.700	---	14.60	22.67	26.92	---	---	---	---	---	---	---	---	1973	86213																						
																								0.25	77.4	4.000	0.256	1.330	1.330	---	14.70	22.82	22.82	---	---	---	---	---	---	---	---				
																								0.25	77.4	4.000	0.256	1.480	1.660	---	12.70	21.18	22.2/ 0.9	23.00	---	---	---	---	---	---	---	---	---		
																								1.00	R. T.	L-T	76.1	20.000	1.000	7.000	8.600	---	7.60	27.29	31.42	---	---	---	---	---	---	---	---	---	
																								1.00	76.1	20.000	1.000	7.000	10.090	---	7.00	25.14	33.14	---	---	---	---	---	---	---	---	---	---		
																								1.00	76.1	20.000	1.000	7.000	9.080	---	7.50	26.93	32.45	---	---	---	---	---	---	---	---	---	---		
T651	P	1.00	R. T.	L-T	76.3	20.000	1.000	7.000	7.600	---	7.50	26.93	28.49	---	---	---	---	---	---	---	---	1973	86213																						
																								1.00	76.3	20.000	1.000	7.000	8.850	---	7.60	27.29	32.33	---	---	---	---	---	---	---	---				
																								1.00	76.3	20.000	1.000	7.000	8.900	---	7.50	26.93	30.92	---	---	---	---	---	---	---	---	---			
																								1.00	76.3	20.000	1.000	7.000	8.400	---	7.60	27.29	31.06	---	---	---	---	---	---	---	---	---			
																								1.00	77.5	20.000	1.000	7.000	8.450	---	6.90	24.78	28.32	---	---	---	---	---	---	---	---	---			
																								1.00	77.5	20.000	1.000	7.000	8.500	---	7.30	26.21	30.10	---	---	---	---	---	---	---	---	---			
																								1.00	77.5	20.000	1.000	7.000	7.910	---	6.30	22.62	26.2/ 1.5	24.63	---	---	---	---	---	---	---	---			
																								0.12	R. T.	T-L	77.4	3.000	0.127	1.100	1.280	---	14.50	20.81	23.23	---	---	---	---	---	---	---	---	---	---
																								0.12	77.4	3.000	0.126	1.090	1.280	---	15.70	22.39	25.15	---	---	---	---	---	---	---	---	---	---	---	
																								0.12	77.4	3.000	0.126	1.100	1.140	---	15.90	22.82	23.40	---	---	---	---	---	---	---	---	---	---		
																								0.12	77.4	3.000	0.128	1.100	1.280	---	14.80	21.24	23.71	---	---	---	---	---	---	---	---	---	---		
																								0.12	77.5	3.000	0.127	1.080	1.180	---	15.70	22.25	23.67	---	---	---	---	---	---	---	---	---	---		
0.12	77.5	3.000	0.127	1.080	1.350	---	17.10	24.24	28.56	---	---	---	---	---	---	---	---	---	---																										

BUCKLING OF CRACK EDGES NOT RESTRAINED

TABLE 7.2.2.2 (Con't)

CONDITION	ALUMINUM		2020		K(I,C)		CRACK LENGTH CROSS STRESS										K(I,C) STAN		K(I,C) MEAN DEV		K(I,C) STAN		K(I,C) MEAN DEV		DATE REFER		
	FORM	THICK (IN)	TEST TEMP (F)	SPEC OR	YIELD STR (KSI)	SPECIMEN		W	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	K(I,C) (KSI*SQRT IN)	STAN	MEAN	DEV	K(I,C) (KSI*SQRT IN)	K(I,C) (KSI*SQRT IN)	STAN	MEAN	DEV	DATE	REFER		
						W	B																			2A(O)	2A(F)
T651	S	0.12	R.T.	T-L	77.5	3.000	0.127	1.090	1.170	---	17.00	24.25	25.48	1973	86213												
		0.12			77.5	3.000	0.126	1.080	1.110	---	15.90	22.54	22.97	1973	86213												
		0.12			78.4	3.000	0.127	1.070	1.150	---	14.60	20.57	21.62	1973	86213												
		0.12			78.4	3.000	0.127	1.090	1.090	---	14.60	20.83	20.83	1973	86213												
		0.12			78.4	3.000	0.127	1.080	1.320	---	14.90	21.12	24.44	1973	86213												
T651	P	0.25	R.T.	T-L	78.0	3.000	0.256	1.120	1.140	---	10.70	15.95	15.74	1973	86213												
		0.25			78.0	3.000	0.256	1.000	1.000	---	15.00	20.20	20.20	1973	86213												
		0.25			78.0	3.000	0.256	1.140	1.140	---	10.70	15.74	15.74	1973	86213												
T651	P	0.25	R.T.	T-L	78.0	4.000	0.256	1.330	1.330	---	13.50	20.96	20.96	1973	86213												
		0.25			78.0	4.000	0.257	1.330	1.330	---	13.40	20.80	20.80	1973	86213												
T651	P	1.00	R.T.	T-L	77.4	20.000	1.000	7.000	7.000	---	5.40	19.39	19.39	1973	86213												
		1.00			77.4	20.000	1.000	7.000	7.000	---	5.60	20.11	20.11	1973	86213												
		1.00			77.4	20.000	1.000	7.000	7.000	---	5.90	21.19	21.19	1973	86213												
		1.00			77.4	20.000	1.000	7.000	7.000	---	5.60	20.11	20.11	1973	86213												
		1.00			77.5	20.000	1.000	7.000	7.000	---	5.40	19.39	19.39	1973	86213												
		1.00			77.5	20.000	1.000	7.000	7.000	---	5.40	19.39	19.39	1973	86213												
		1.00			77.5	20.000	1.000	7.000	7.000	---	5.40	19.39	19.39	1973	86213												
		1.00			77.5	20.000	1.000	7.000	7.000	---	5.50	19.75	19.75	1973	86213												
		1.00			78.4	20.000	1.000	7.000	7.000	---	5.20	18.67	18.67	1973	86213												
		1.00			78.4	20.000	1.000	7.000	7.000	---	5.30	19.03	19.03	1973	86213												
	1.00			78.4	20.000	1.000	7.000	7.000	---	5.10	18.31	18.31	1973	86213													
	1.00			78.4	20.000	1.000	7.000	7.000	---	5.10	18.31	18.31	1973	86213													

BUCKLING OF CRACK EDGES NOT RESTRAINED

TABLE 7.2.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.2.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2020			
CONDITION: T6					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K MIN	A:	16.10	29.5		
	B:				
	C:				
	D:				
		20.00	104.		
DELTA K MAX	A:	24.15	415.		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		27.51			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	2			
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T6
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.00
 FREQUENCY: 13.30

YIELD STRENGTH: 78.4 KSI
 ULT. STRENGTH: 84.7 KSI
 SPECIMEN THK: 0.125- 0.126"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 86213

ALUM.
ALLOY

2020

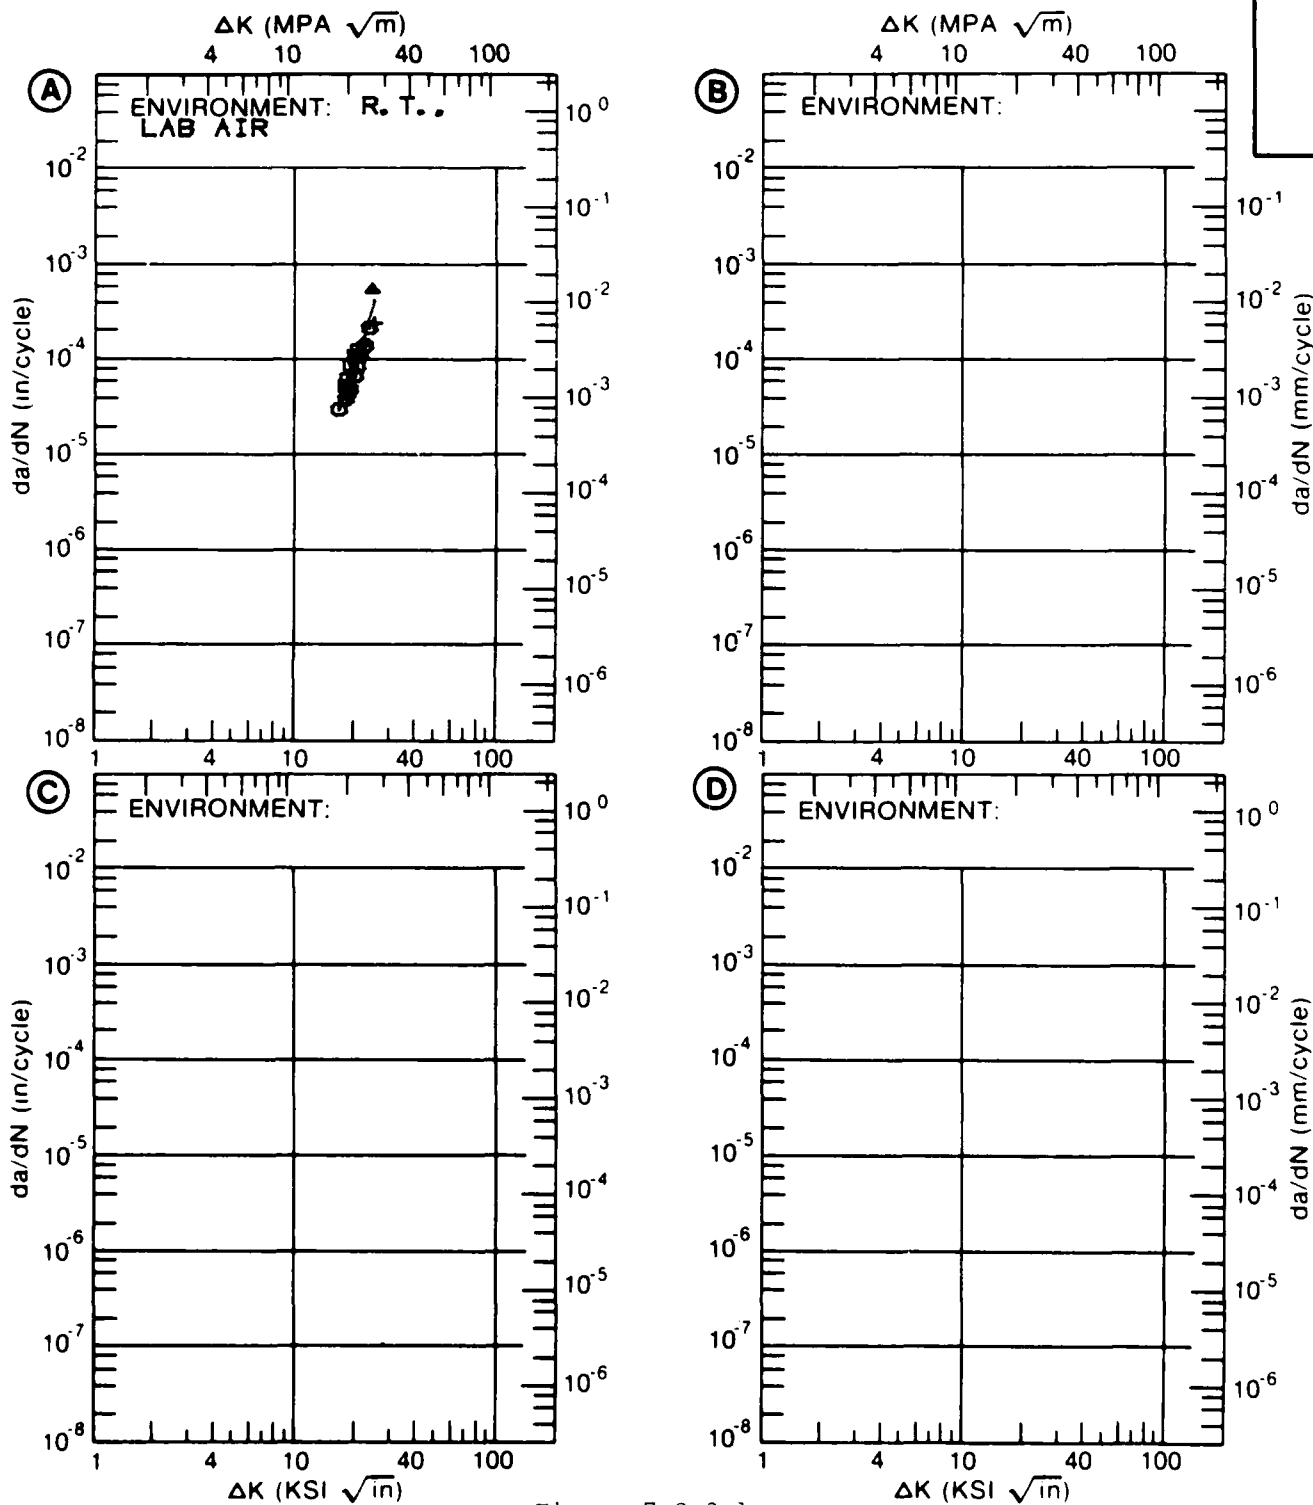


Figure 7.2.3.1

TABLE 7.2.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.2.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2020			
CONDITION: T651					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.	E= R. T. H. H. A. - 25HZ		
DELTA K	A: 3.15	.0956			
MIN	B: 3.72		.157		
	C:				
	D:				
	3.50	.205			
	4.00	.352	.203		
	5.00		.396		
	6.00		.704		
	7.00		1.25		
	8.00		2.12		
	9.00		3.33		
	10.00		4.81		
	13.00		9.17		
DELTA K	A: 4.98	.574			
MAX	B: 15.96		29.4		
	C:				
	D:				
ROOT MEAN SQUARE		17.57	12.36		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25		1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T651
 FORM: 1.28" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY:

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.248- 0.250"
 SPECIMEN WIDTH: 2.500- 2.501"
 REFERENCES: AL002

ALUM. ALLOY
2020

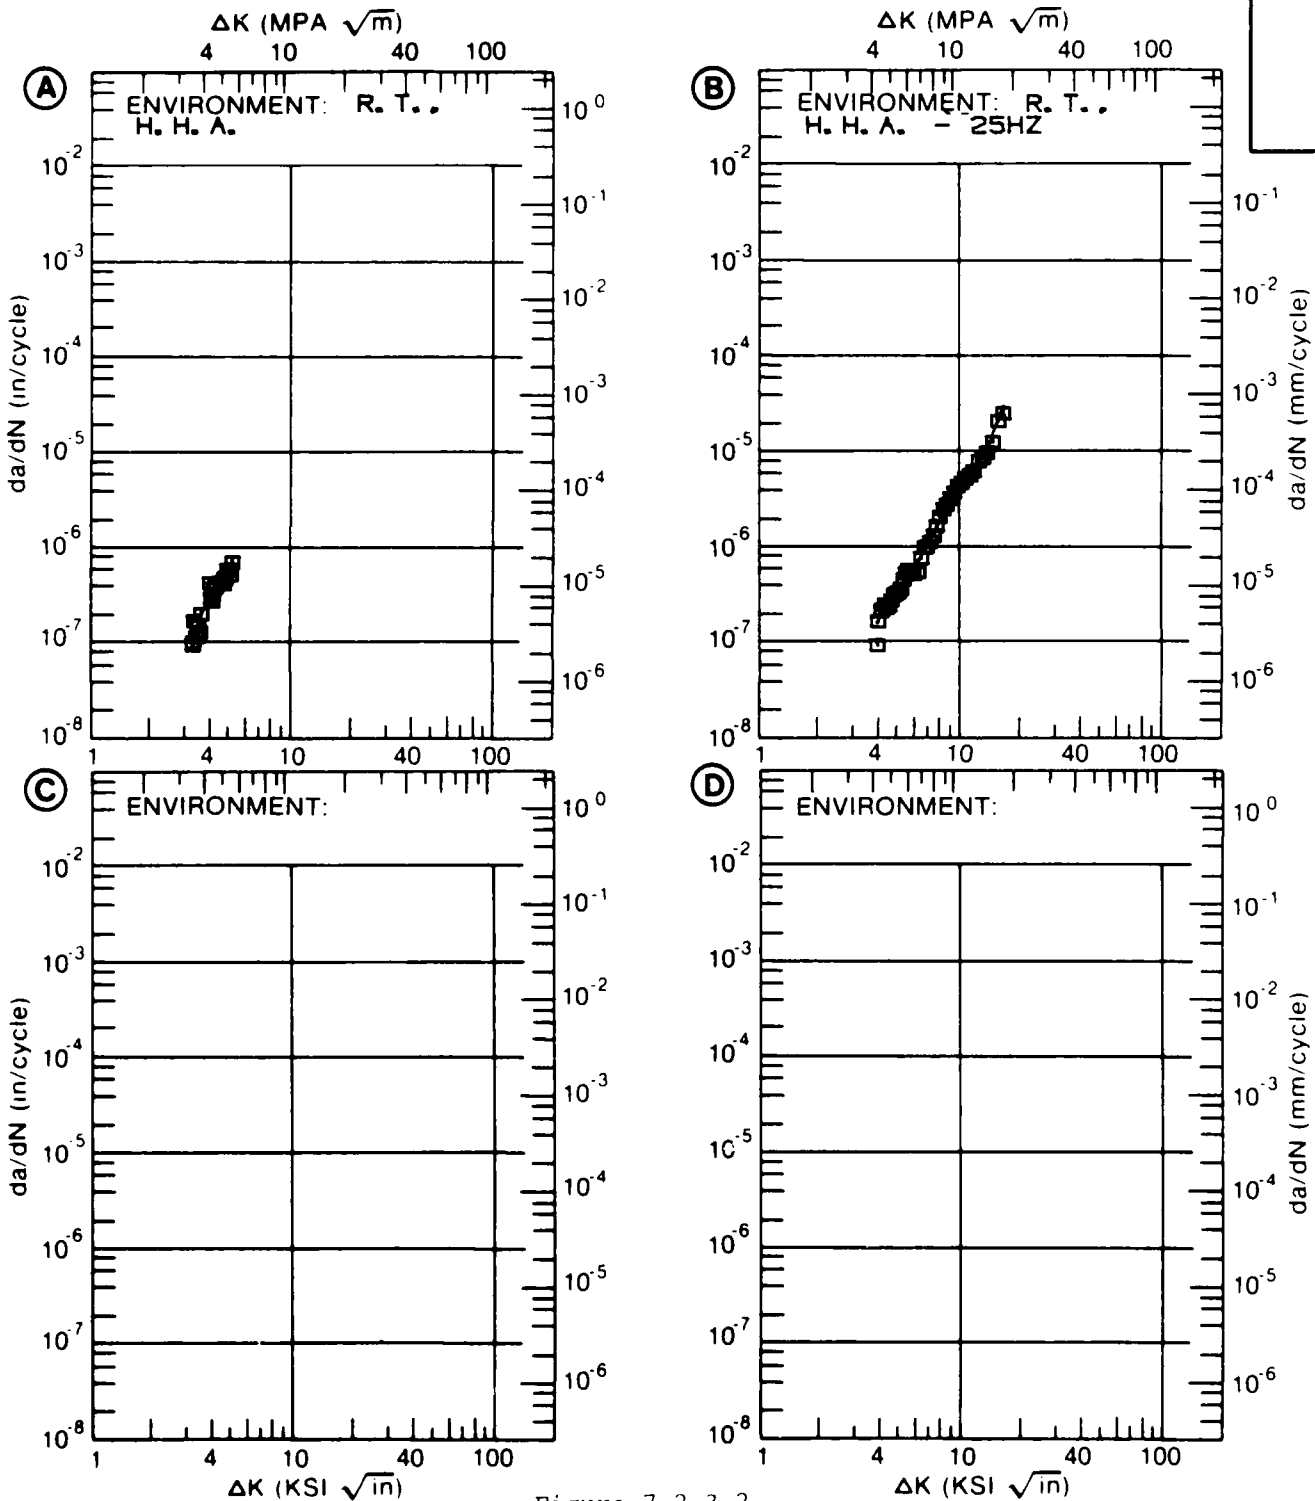


Figure 7.2.3.2

TABLE 7.2.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.2.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2020			
CONDITION: T651					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		H. H. A.			
DELTA K MIN	A:	2.68	.027		
	B:	0			
	C:				
	D:				
		3.00	.0598		
		3.50	.147		
		4.00	.282		
		5.00	.706		
		6.00	1.42		
		7.00	2.67		
	8.00	4.99			
	9.00	9.49			
	10.00	18.5			
DELTA K MAX	A:	11.13	40.8		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		43.54			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T651
 FORM: 1.28" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 25.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.248"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: AL002

ALUM.
ALLOY

2020

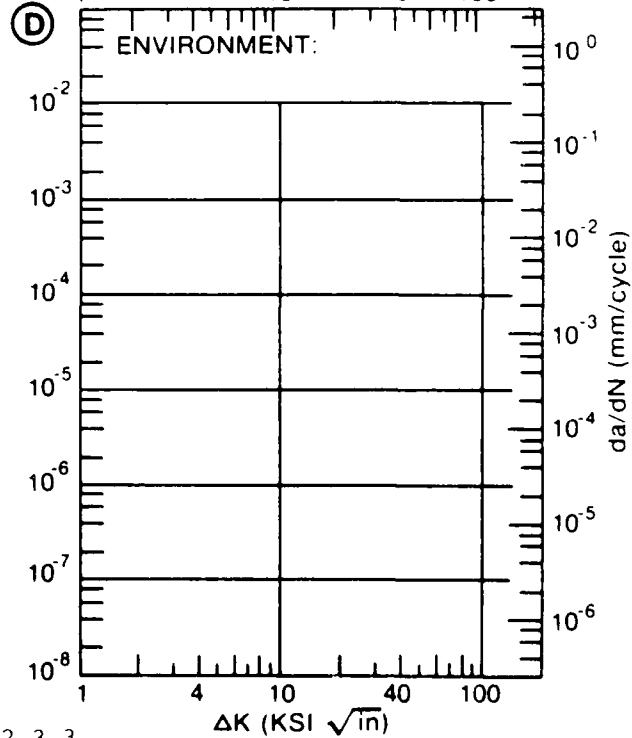
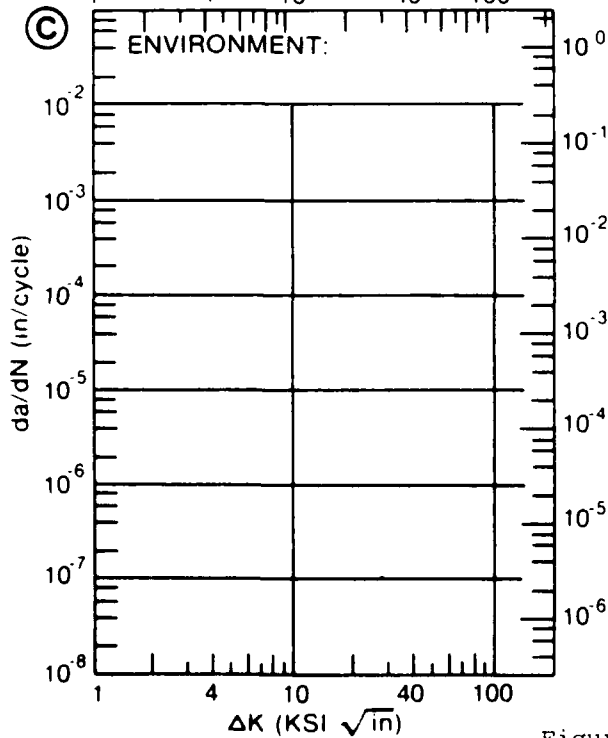
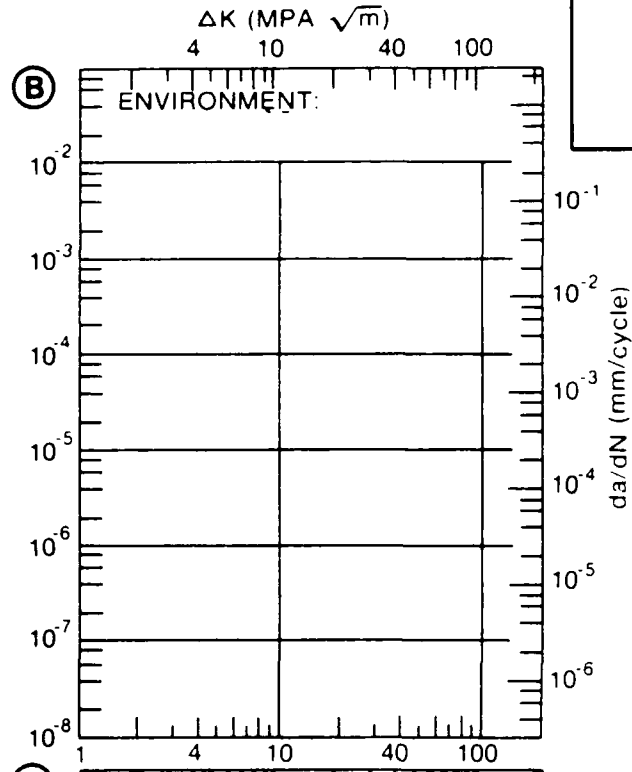
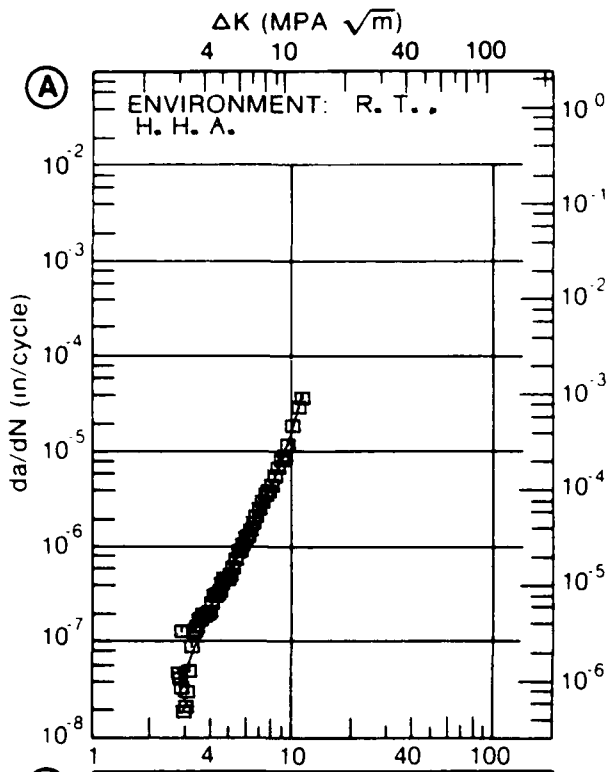


Figure 7.2.3.3

TABLE 7.2.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.2.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2020			
CONDITION: T651					
ENVIRONMENT: R. T., LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		R=-0.50	R=+0.00		
DELTA K	A: 5.76	.549			
MIN	B: 5.25		.0908		
	C:				
	D:				
	6.00	.580	.254		
	7.00	.840	.672		
	8.00	1.35	1.35		
	9.00	2.16	2.28		
	10.00	3.33	3.45		
	13.00	9.63	8.55		
	16.00	21.1	17.4		
DELTA K	A: 18.95	64.6			
MAX	B: 16.95		21.5		
	C:				
	D:				
ROOT MEAN SQUARE		36.60	32.02		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1	1		
RATIO	0.8-1.25	2	3		
SUMMARY	1.25-2.0	1	1		
(NP/NA)	>2.0				

CONDITION/HT: T651
 FORM: 1.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 5.20
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 76.2 KSI
 ULT. STRENGTH: 81.7 KSI
 SPECIMEN THK: 0.748- 0.754"
 SPECIMEN WIDTH: 2.997- 3.003"
 REFERENCES: 86213

ALUM.
 ALLOY
 2020

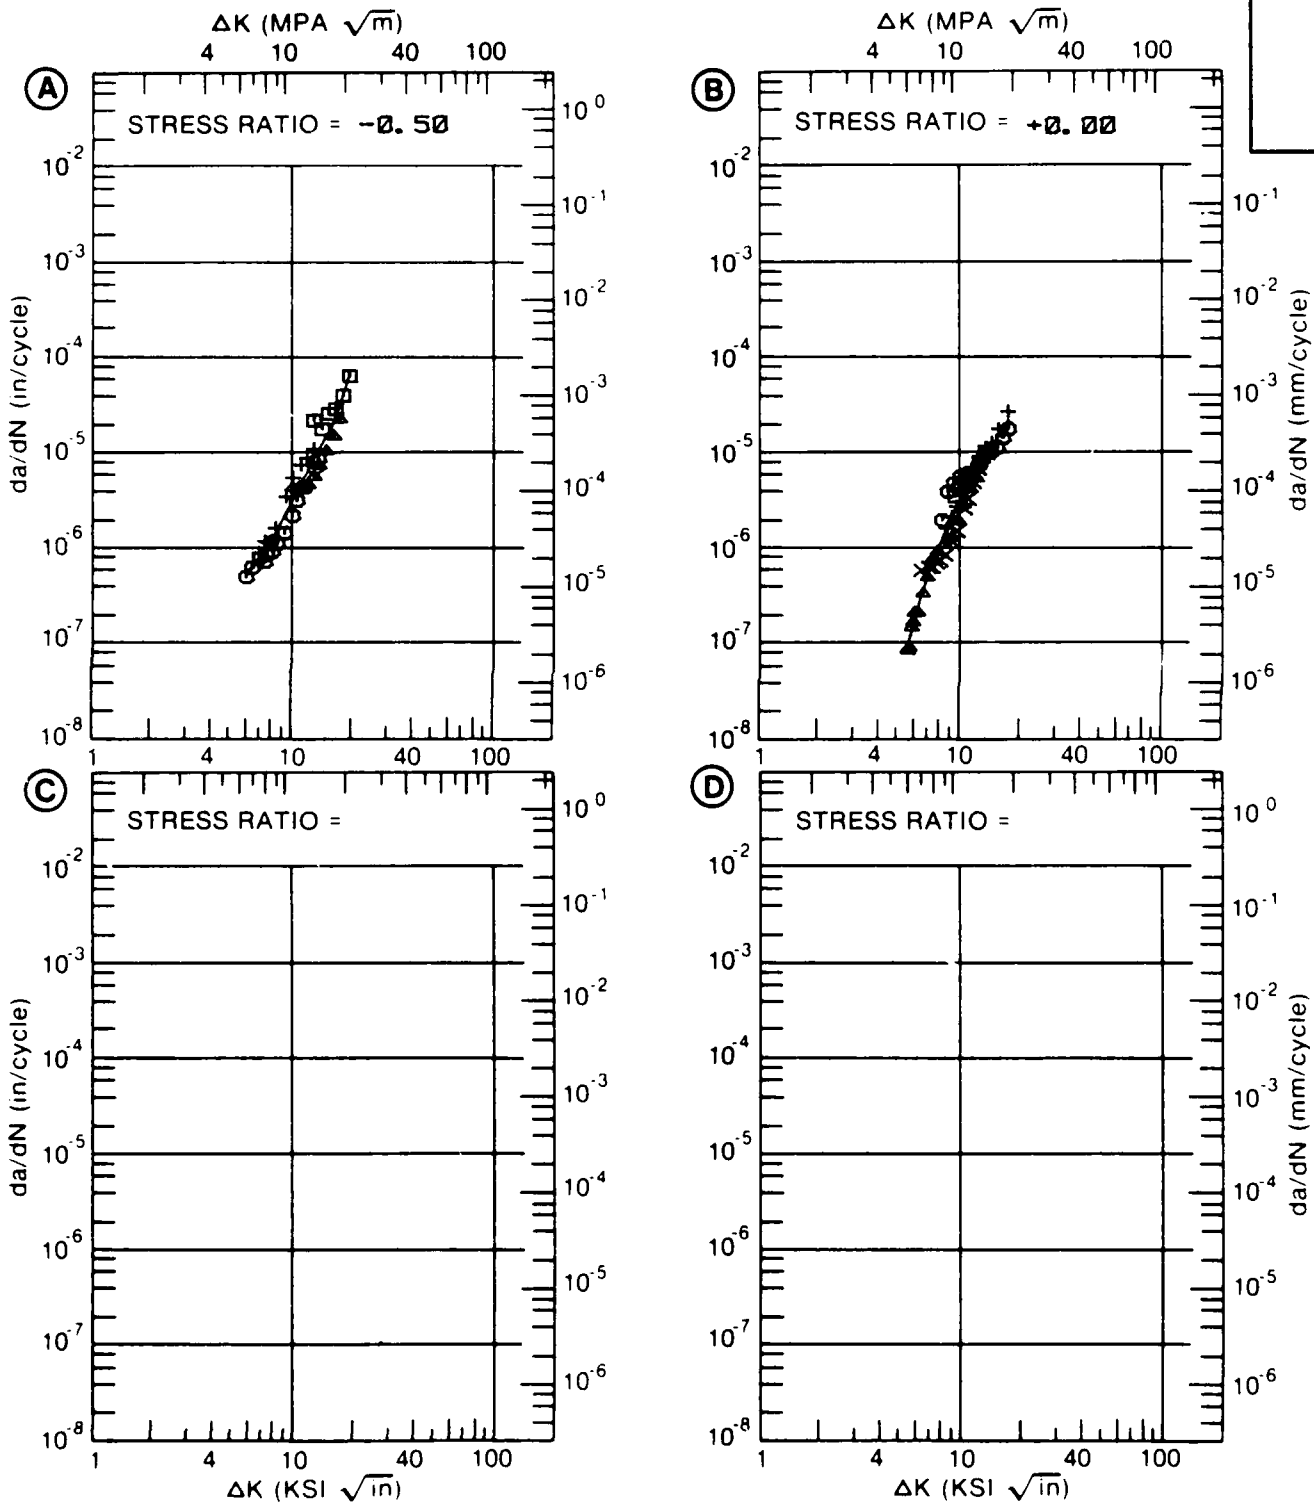


Figure 7.2.3.4

TABLE 7.2.3.5

ALUMINUM		2020		K (TSCC)									
CONDITION	PRODUCT-- FORM THICK (IN)	TEST SPEC OR STR (KSI)	ENVIRONMENT	WIDTH (IN)	THICKNESS (IN)	DESIGN (*S0)	CRACK LENGTH (IN)	K (TSCC)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER	
				W	B	A		(KSI*SQRT IN)					
T651	P	1.00	R. T.	S-L	60.0	3.5	PCT NAACL	4.000	1.000	DCB	13.00	9.00	1968 64331

TABLE 7.3.2.1

ALUMINUM		2020 (ALCLAD)		K(C)		CRACK LENGTH GROSS STRESS																				
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC TEMP OR (F)	YIELD STR (KSI)	--SPECIMEN--		INIT		FINAL		ONSET		MAX		K (APP)		STAN		K (C)		STAN DEV	REFER					
				W	B	(IN)	(IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)			(KSI)	(KSI)			
T6	S	0.06	68.0	R. T.	L-T	0.062	4.000	4.130	---	13.30	34.72	---	---	---	---	---	---	---	---	---	---	---				
						0.062	3.970	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---		
						0.063	3.970	4.090	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
T6	S	0.12	68.6	R. T.	L-T	0.123	0.980	1.570	---	24.00	32.16	---	---	---	---	---	---	---	---	---	---	---				
						0.123	0.985	1.550	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---		
						0.122	0.988	1.350	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
						0.122	1.100	1.410	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
						0.122	1.270	1.610	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
						0.123	1.000	1.260	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
T6	S	0.06	67.2	R. T.	T-L	0.064	4.020	---	---	12.10	31.68	---	---	---	---	---	---	---	---	---	---					
						0.064	4.010	4.400	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---			
						0.064	4.000	4.200	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---		
T6	S	0.12	68.4	R. T.	T-L	0.122	0.993	1.540	---	18.90	25.37	---	---	---	---	---	---	---	---	---	---	---				
						0.122	0.997	1.540	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---		
						0.122	0.987	1.500	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
						0.122	0.983	1.500	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
						0.123	1.000	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
						0.121	1.100	1.380	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
T6	S	0.12	68.4	R. T.	T-L	0.123	1.000	1.000	---	15.90	22.82	---	---	---	---	---	---	---	---	---	---	---				
						0.123	1.000	1.000	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---		
						0.122	1.110	1.310	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	

BUCKLING OF CRACK EDGES NOT RESTRAINED

TABLE 7.4.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 2021 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD DEVIATION		PLATE
	(KSI SQRT(IN))	(NUMBER OF SPECIMENS)	
T81	27 0 ± 0.5 (3)	---	S-L
T81 REPAIR WELD + AGE WITH 2319 FILLER WIRE	---	15 8 ± 0.7 (6)	---
T81 WELD + AGE WITH 2317 FILLER WIRE	---	19 4 ± 2.7 (9)	---

TABLE 7.4.2.1

CONDITION	ALUMINUM										K(1C)	
	2021					2.5*					K(1C) MEAN (IN)	K(1C) STAN DEV (IN)
	---PRODUCT--- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	CRACK THICK (IN)		
T81	P	1.00	R.T.	L-T	61.2	1.990	0.996	CT	0.937	0.47	26.60	1972 84363
		1.00			61.2	2.000	0.995	CT	0.933	0.50	27.50	1972 84363
		1.00			61.2	2.000	0.993	CT	0.961	0.48	26.80	1972 84363
T81 REPAIR WELD + AGE WITH 2319 FILLER WIRE	P	1.00	R.T.	T-L	---	2.000	1.000	CT	1.000	0.19	15.90	1970 80073
		1.00			---	2.000	1.000	CT	1.010	0.14	15.20	1970 80073
		1.00			---	2.000	1.000	CT	0.990	0.14	15.20	1970 80073
		1.00			---	2.000	1.000	CT	1.030	0.16	16.00	1970 80073
		1.00			---	2.000	1.000	CT	1.040	0.14	15.20	1970 80073
		1.00			---	2.000	1.000	CT	1.020	0.18	17.00	1970 80073
T81 WELD + AGE WITH 2319 FILLER WIRE	P	1.00	R.T.	T-L	---	2.000	1.000	CT	1.040	0.19	17.60	1970 80073
		1.00			---	2.000	1.000	CT	1.030	0.20	18.40	1970 80073
		1.00			---	2.000	1.000	CT	0.990	0.16	16.40	1970 80073
		1.00			---	2.000	1.000	CT	1.020	0.32	22.90	1970 80073
		1.00			---	2.000	1.000	CT	1.080	0.22	18.90	1970 80073
		1.00			---	2.000	1.000	CT	1.050	0.33	23.20	1970 80073
		1.00			---	2.000	1.000	CT	1.040	0.18	17.20	1970 80073
		1.00			---	2.000	1.000	CT	1.010	0.31	22.60	1970 80073
		1.00			---	2.000	1.000	CT	1.040	0.19	17.50	1970 80073
T8151	P	1.00	84	L-T	64.8	1.500	0.749	CT	0.706	0.32	23.10	1973 86213
		1.00			64.8	1.500	0.749	CT	0.714	0.29	22.00	1973 86213
T8151	P	1.00	84	T-L	63.4	1.500	0.731	CT	0.726	0.23	19.10	1973 86213

TABLE 7.4.3.1

CONDITION	--PRODUCT--		TEST TEMP (F)	SPEC OR STR (KSI)	YIELD (KSI)	ENVIRONMENT	ALUMINUM		W	SPECIMEN		W	THICK (IN)	DESIGN (**SG)	CRACK		K (ISCC)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)					WIDTH (IN)	THICK (IN)		LENGTH (IN)	A				B						
T81	P	2.50	R.T.	S-L	59.1	INDUSTRIAL ATM	2.000	1.000	CT	---	19.60	19.00	---	1973	86688						
T81	P	2.50	R.T.	S-L	59.1	SALT-DICHROMATE-ACETATE	2.000	1.000	CT	---	19.60	19.00	---	1973	86688						
T81	P	2.50	R.T.	S-L	59.1	SEACOAST ATM	2.000	1.000	CT	---	19.60	19.00	---	1973	86688						
T81 OVERHEATED WELD	P	1.00	R.T.	S-L	18.3	3.5 PCT NAACL	2.500	1.000	MDL	---	14.00	11.30	>	4320	1970 80073						
T81 REPAIRED WELD AGED 16HR FUSION LINE	P	1.00	R.T.	S-L	24.7	3.5 PCT NAACL	2.500	1.000	MDL	---	14.00	7.70	>	4320	1970 80073						
T81 REPAIRED WELD AGED 16HR CENTER LINE	P	1.00	R.T.	S-L	24.7	3.5 PCT NAACL	2.500	1.000	MDL	---	14.00	> 10.30	>	4320	1970 80073						
T81 REPAIRED WELD AGED 16HR AFFECTED ZONE	P	1.00	R.T.	S-L	28.0	3.5 PCT NAACL	2.500	1.000	MDL	---	14.00	11.90	>	4320	1970 80073						
T81 WELDED AGED 16HR 325F HEAT AFFECTED ZONE	P	1.00	R.T.	S-L	25.0	3.5 PCT NAACL	2.500	1.000	MDL	---	14.00	13.30	>	4560	1970 80073						
T81 WELDED AGED 16HR 325F WELD CENTER LINE	P	1.00	R.T.	S-L	23.4	3.5 PCT NAACL	2.500	1.000	MDL	---	17.00	7.20	>	4320	1970 80073						
T81 WELDED AGED 16HR 325F FUSION LINE	P	1.00	R.T.	S-L	23.4	3.5 PCT NAACL	2.500	1.000	MDL	---	17.00	8.50	>	4320	1970 80073						

TABLE 7.5.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 2024 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD DEVIATION		(NUMBER OF SPECIMENS)
	(KSI)	(IN)	
	<u>PLATE</u>		
T351	35 0 ± 7 1 (2)	-----	-----
T851	27 3 ± 2 4 (65)	20 7 ± 1 9 (63)	-----
	<u>FORGING</u>		
	<u>L-T</u>	<u>I-L</u>	<u>S-L</u>
T852	29 2 ± 5 2 (24)	18 9 ± 2 6 (16)	15 9 ± 0 8 (8)
	<u>EXTRUSION</u>		
	<u>L-T</u>	<u>I-L</u>	<u>S-L</u>
T351	-----	25 0 ± 0 9 (5)	-----
T3511	38 0 ± 2 6 (4)	-----	-----
T8510	30 4 ± 2 7 (3)	16 5 ± 1 0 (3)	15 7 ± 1 4 (3)
T8511	24 1 ± 0 4 (2)	16 0 ± 0 0 (2)	-----

TABLE 7.5.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-S

ENVIRONMENT H H A
A T R I

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
T851	PLATE	0.10	20.00								0.50
T851	PLATE	0.10	30.00								0.34
T851	PLATE	0.10	20.00								5.84

TABEL 7.5.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINIUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT DRY AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT (IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 10 20 50 100	
TB1	SHEET	-0.25	6.00		4.17 46.1
TB1	SHEET	0.10	6.00		5.65 52.2
TB1	SHEET	0.30	6.00		10.2 66.4
TB1	SHEET	0.50	6.00		1.26 14.8 268

TABLE 7.5.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT

L H A
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
T81	SHEET	0.08	1.00				5.82	79.2		
T81	SHEET	0.08	6.00				4.78	71.8		
T81	SHEET	0.30	6.00				8.64	193		
T81	SHEET	0.50	6.00				1.26	17.6	686	
T851	PLATE	0.08	1.00	SPEC THK=0.50"			5.52			
T851	PLATE	0.08	1.00	SPEC THK=1.00"			7.37			
T851	PLATE	0.08	6.00	SPEC THK=1.00"			8.93			
T851	PLATE	0.30	1.00				12.9			
T852	FORGING	0.08	0.10				6.88			
T852	FORGING	0.08	1.00	SPEC THK=1.00"			1.06	9.01		
T852	FORGING	0.08	6.00	SPEC THK=0.25"-0.50"			3.72	27.4		

TABLE 7.5.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT AIR AT - 65 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
T351	SHEET	0.50	---	2.5 5 10 20 50 100	0.35 19.7
T351	SHEET	0.80	---		20.4
T351	PLATE	0.00	1.00-2.00		2098

TABLE 7.5.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT LAB AIR AT R T

CONDITION	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
T3	SHEET	0.00	13.30						28.6	
T3	SHEET	0.20	10.00		0.21		4.72	27.9		
T3	SHEET	0.33	3.33					188		
T3	PLATE	-1.00	20.00			9.29	70.3			
T3	PLATE	-0.50	20.00		0.14	13.2	67.2			
T3	PLATE	0.05	20.00			2.36				
T31	SHEET	0.00	3.00-6.00				4.15	44.0		
T31	SHEET	0.40	3.00-6.00					163		
T31	SHEET	0.80	3.00-6.00				39.2			
T31	PLATE	-1.00	1.00-16.00					74.6		
T31	PLATE	-1.00	3.00-5.00			0.27	5.44	41.3		
T31	PLATE	-0.50	3.00-5.00			0.25	7.67	47.2		
T31	PLATE	0.00	1.00-16.00						2324	
T31	PLATE	0.00	5.00-20.00			0.15				
T31	PLATE	0.01	1.00-10.00			0.20	7.09	39.8		
T31	PLATE	0.01	20.00			5.98	52.1			

TABLE 7.5.1.6 (Con't)

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINIUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT LAP AIR AT R T

COND: IOR/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
T301	PLATE	0.10	3.00					55.0		
T351	PLATE	0.10	20.00					9.62		
T351	PLATE	0.30	20.00					10.4		
T351	PLATE	0.33	25.00					7.88		
T351	PLATE	0.40	1.00-10.00			0.70	11.7			
T351	PLATE	0.40	1.00-16.00					232		
T351	PLATE	0.40	5.00-20.00			0.47				
T351	PLATE	0.50	20.00					13.1		
T351	PLATE	0.60	1.00-10.00			0.88	13.8			
T351	PLATE	0.60	20.00					14.4		
T351	PLATE	0.80	1.00-16.00	SPEC THK=0.189-0.250"				40.9		
T351	PLATE	0.80	5.00-20.00	SPEC THK=0.250"				1.41		
T351	PLATE	0.80	1.00-10.00			1.71	23.2			
T3511	EXTRUSION	0.05	9.00					127		
T3511	EXTRUSION	0.50	9.00					0818		

TABLE 7.5.1.6 (Con't)

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L T

ENVIRONMENT LAB AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))			FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)		
				2.5	5	10	20	50	100
T42	PLATE	-1.00	10.00		5.41	44.3	2809		
T42	PLATE	0.02	10.00		4.25	23.6	1131		
T42	PLATE	0.50	10.00		424	7.89	42.5		
T81	SHEET	0.05	2.00				68.1		
T81	SHEET	0.40	2.00				106		
T81	PLATE	0.02	1.00-10.00				3.90	57.0	

TABLE 7.5.1.7

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION	L-T	ENVIRONMENT	AIR AT	200 F	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
CONDITION/HI	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2 5 5 10 20 50 100
T351	PLATE	0.01	20.00		0.92
T351	PLATE	0.10	20.00		0.70
T351	PLATE	0.30	20.00		1.08
T351	PLATE	0.50	20.00		1.35
T351	PLATE	0.60	20.00		1.43

TABLE 7.5.1.8

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT AIR AT 300 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (Hz)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
T351	PLATE	0.01	20.00		7.43
T351	PLATE	0.10	20.00		9.35
T351	PLATE	0.30	20.00		12.3
T351	PLATE	0.50	20.00		13.6
T351	PLATE	0.60	20.00		15.6

TABLE 7.5.1.9

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION 1-1

ENVIRONMENT AIR AT 400 F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
T351	PLATE	0.01	20.00							6.89
T351	PLATE	0.10	20.00							10.6
T351	PLATE	0.30	20.00							12.4
T351	PLATE	0.50	20.00				1.47	14.6		
T351	PLATE	0.50	20.00				1.56	17.6		

TABLE 7.5.1.10

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS
SPECIMEN
ORIENTATION L-T

ENVIRONMENT H H A
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2 5	5	10	20	50	100
T3	SHEET	0.05	2.00							35.3
T351	SHEET	0.00	9.00				4.09			
T351	PLATE	0.33	25.00			0.35	1.08	96.4		
T351	PLATE	0.33	25.00			1.10	1.10			
T351	SHEET	0.70	9.00			0.63	5.42			
T3511	EXTRUSION	0.05	9.00			0.06	1.05			
T3511	EXTRUSION	0.50	9.00			0.43	4.35	62.3		
T3511	EXTRUSION	0.50	9.00		0.05					
T62	SHEET	0.10	1.00			0.31	4.68			
T62	SHEET	0.30	1.00			0.46	1.01	96.4		

TABLE 7.5.1.10 (Con't)

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION 1-7

ENVIRONMENT H H A
A T R 7

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
T81	SHEET	-0.25	1.00			0.28	6.45	51.3		
T81	SHEET	0.10	0.10				43.9			
T81	SHEET	0.10	1.00				8.15	70.1		
T81	SHEET	0.30	1.00			1.04	15.2			
T81	SHEET	0.50	1.00			1.50	17.2			
T851	PLATE	0.33	25.00			0.92	12.2			

TABLE 7.5.1.11

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT J P 4 AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
TB1	SHEET	0.0P	1.00	2 5 5 10 20 50 100	7.53 72.0
TB51	PLATE	0.0R	1.00		8.55 108

TABLE 7.5.1.12
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 ALUMINUM 2024

TEST CONDITIONS		ENVIRONMENT		S.T.W		FATIGUE CRACK GROWTH RATES				
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (H7)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
T351	SHEET	0.00	1.00-10.00				3.21			
T351	SHEET	0.33	1.00-10.00					113		
T62	SHEET	0.10	1.00			0.77	7.61			
T62	SHEET	0.50	1.00		0.13	1.43				
T62	SHEET	0.70	1.00			2.05				
T81	SHEET	-0.20	1.00			0.74	11.2			
T81	SHEET	0.08	1.00				8.00	94.0		
T81	SHEET	0.10	1.00			0.36	8.25			
T851	PLATE	0.08	1.00				7.92	112		

TABLE 7.5.1.13

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT H.H.A. AT RT

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))		FATIGUE CRACK GROWTH RATES (MICR/IN CYCLE)			
				2	5	1	50	100	
T851	PLATE	0.10	20.00			0.57	4.87		
T851	PLATE	0.10	20.00			0.63	6.24		
T851	PLATE	0.50	2.00			0.99	11.7		
T851	PLATE	0.50	20.00		0.07	1.13	6.47		

TABLE 7.5.1.14

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION T-S

ENVIRONMENT 3.5% NaCl AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))					FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)				
				2	5	5	10	20	50	100			
T651	PLATE	0.10	20.00			1.18	5.81						
T651	PLATE	0.10	20.00				6.73						
T651	PLATE	0.10	20.00				5.92						
T651	PLATE	0.50	20.00				10.7	265					
T651	PLATE	0.50	20.00			0.96	10.0						

TABLE 7.5.1.15
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION T L

ENVIRONMENT DRY AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
T62	SHEET	0.10	6.00				0.81	11.3		
T62	SHEET	0.30	6.00				0.71	11.3		
T62	SHEET	0.50	6.00		0.04	0.94	1.11			
T81	SHEET	0.25	6.00				3.81	48.3		
T81	SHEET	0.10	6.00				3.51			

TABLE 7.5.1.16
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
 ALUMINUM 2024

TEST CONDITIONS		ENVIRONMENT		L H A		A T R T				
SPECIMEN ORIENTATION	1-L									
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2 5	5	10	20	50	100
T81	SHEET	0.08	1.00-6.00			0.73	4.29	72.8		
T851	PLATE	0.08	1.00						5.90	
T851	PLATE	0.08	6.00						5.45	

TABLE 7.5.1.17

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

TEMPERATURE 70 F

ENVIRONMENT LAB AIR AT RT

CONDITION	PROMET FORM	STRESS RATIO	FREQ (Hz)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
T83	SHEET	0.08	13.00				0.32	21.6		
T84	SHEET	0.10	30.00		0.25					
T85	SHEET	0.13	13.30			7.07	62.6			
T86	SHEET	0.40	30.00		0.94					
T87	SHEET	0.60	30.00		1.22					
T88	FORGING	0.33	5.17				5.50			
T89	SHEET	0.08	0 10-15 00			0.71	5.10	395		
T84	SHEET	0.10	0 10- 40					696		
T85	SHEET	0.13	1 00 10 00					542		
T86	SHEET	0.40	2 00- 9 00				0.60	100		
T87	SHEET	0.60	10 00 13 00		0.99					
T88	SHEET	0.10	10 00-20 00		1.03	10.0				
T89	SHEET	0.40	10 00 15 00		1.23	11.5				
T86	PLATE	0.10	1 00- 5 00						127	
T87	PLATE	0.10	10 00						5.91	

TABLE 7.5.1.18

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 2024

TEST CONDITIONS

TEST SPECIFICATION: MIL-STD-1547-1 ENVIRONMENT: AIR AT 140 F

TEST SPECIFICATION	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
	SM-ET	0.43	5.06-10.00	2.5 3 4 5 6 7 8 9 10 11 12 13 14 15 16 17 18 19 20 25 30 35 40 45 50 55 60 65 70 75 80 85 90 95 100	0.79 1.43
	SM-FT	0.75	5.66-10.00		1.77 3.17

TABLE 7.5.1.19

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN IDENTIFICATION P-C

ENVIRONMENT H H A
AT R (

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
T62	SHEET	0.30	1.00			0.78	11.7			
T62	SHEET	0.50	1.00		0.12	1.26	14.5			
T81	SHEET	-0.25	1.00			4.89	64.7			
T81	SHEET	0.10	1.00			6.37	129			
T81	SHEET	0.50	1.00			1.44	22.2			
T851	PLATE	0.10	20.00			7.38	71.4			
T851	PLATE	0.10	20.00			0.50	9.04			
T851	PLATE	0.50	20.00		0.17	1.31	17.2			

TABLE 7.5.1.20

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION 1-L

ENVIRONMENT 3.5% NaCl
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
T851	PLATE	0.10	0 10-10 00		18.2
T851	PLATE	0.10	20.00		1.47 11.1 126
T851	PLATE	0.10	20.00		0.91 9.93
T851	PLATE	0.50	20.00		0.21 2.28 22.4

TABLE 7.5.1.21

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 2024

TEST CONDITIONS

SPECIMEN ORIENTATION 1-L

ENVIRONMENT S.T.W. AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))				FATIGUE CRACK GROWTH RATES (MICR IN/CYCLE)			
				2	5	10	20	50	100		
T62	SHEET	-0.25	1.00			0.86	4.87				
T62	SHEET	0.10	1.00			0.69	5.87				
T62	SHEET	0.30	1.00			1.24	17.0				
T62	SHEET	0.50	1.00			2.83	25.7				

T81	SHEET	0.08	1.00-6.00				6.90	96.3			
T81	SHEET	0.10	1.00			0.39	7.27	101			

T852	FORGING	0.08	1.00				5.19				

TABLE 7.5.2.1

CONDITION	ALUMINUM										K(IIC)		DATE	REFER		
	--PRODUCT--		TEST SPECIMEN		YIELD STRENGTH		WIDTH THICK		SPECIMEN		CRACK LENGTH (IN)	2.5* K(IIC)/TYS)**2 (IN)			K(IIC) MEAN (KSI*SQRT IN)	K(IIC) STAN DEV (IN)
	FORM	THICK (IN)	THICK (IN)	ORIENT (F)	STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN (IN)	M	B						
T351	P	2.50	R.T.	L-T	53.8	2.000	1.000	CT	0.995	0.78	30.00	35.0/	7.1	1973 86213		
		3.00			54.5	4.000	2.000	NB	---	---	40.00			1972 82878		
T351	P	2.50	85	L-T	55.9	2.000	1.000	CT	1.032	0.63	28.10			1973 86213		
		2.50			55.9	2.000	1.000	CT	1.001	0.60	27.40	27.8/	0.9	1973 86213		
T351	P	2.00	R.T.	T-L	43.8	4.010	2.000	CT	2.147	1.51	34.00			1973 86213		
T351	P	1.00	84	T-L	49.0	1.500	0.749	CT	0.749	0.72	26.30			1973 86213		
		1.00			49.0	1.500	0.750	CT	0.755	0.74	26.60	26.5/	0.2	1973 86213		
T351	P	3.00	R.T.	S-T	64.0	2.500	1.250	CT	---	0.30	22.00			1974 90011		
		3.00			64.0	2.500	1.250	CT	---	0.27	21.00			1974 90011		
		3.00			64.0	2.500	1.250	CT	---	0.27	21.00	21.3/	0.6	1974 90011		
T351	P	2.50	85	S-L	44.8	2.000	0.999	CT	0.928	0.59	21.80			1973 86213		
T351	P	2.50	90	S-L	42.4	2.040	1.000	CT	1.021	0.50	18.90			1973 86213		
T351	E	3.00	R.T.	T-L	41.8	2.990	1.498	CT	1.561	0.92	25.30			1973 86213		
		3.00			41.8	2.990	1.498	CT	1.555	0.93	25.30			1973 86213		
		5.00			43.4	2.990	1.500	CT	1.558	0.73	23.40			1973 86213		
		3.00			43.5	3.000	1.500	CT	1.579	0.83	25.10			1973 86213		
		3.00			43.5	3.000	1.499	CT	1.562	0.86	25.30	25.0/	0.9	1973 86213		
T351	E	3.50	82	T-L	38.7	2.000	1.000	CT	1.048	0.95	23.80			1973 86213		
		5.00			41.1	3.000	1.498	CT	1.528	0.88	24.40			1973 86213		
		5.00			41.1	3.000	1.499	CT	1.514	0.85	24.00	24.1/	0.3	1973 86213		
T351	E	3.00	82	S-L	41.7	2.000	0.999	CT	1.017	0.72	22.40			1973 86213		
		3.00			41.7	2.000	1.000	CT	1.012	0.63	21.00			1973 86213		
		3.00			42.8	2.000	1.000	CT	0.988	0.73	23.20			1973 86213		
		3.00			42.8	2.000	1.000	CT	1.007	0.75	23.90	22.5/	1.1	1973 86213		
T351	FB	3.50	82	T-L	41.5	2.000	0.999	CT	1.050	0.94	25.50			1973 86213		
		3.50			41.5	2.000	1.000	CT	1.045	0.92	25.20			1973 86213		
		5.00			44.5	3.000	1.500	CT	1.594	0.75	24.40			1973 86213		
		5.00			44.5	3.000	1.500	CT	1.506	0.80	25.10			1973 86213		
		3.00			45.7	3.000	1.500	CT	1.504	0.63	23.00			1973 86213		

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	SPECIMEN WIDTH (IN)		DESIGN	CRACK LENGTH (IN)	CRACK 2.9% (K(1C)/TYS)**2 (KSI*SQRT IN)	K(1C) MEAN DEV (K(1C) STAN DEV)	DATE	REFER	
	PRODUCT-- FORM	THICK (IN)			THICK (IN)	THICK (IN)							A
T351	FB	3.00	82	45.7	3.000	1.500	CT	1.480	0.69	24.00	24.5/	0.9	1973 86213
T351	FB	3.00	82	42.1	1.990	1.002	CT	0.963	0.75	23.00			1973 86213
		3.00		42.1	1.990	1.001	CT	0.970	0.73	22.70	22.9/	0.2	1973 86213
T3511	E	---	R.T.	61.2	---	1.200	--	---	1.06	39.90			1978 BM007
		---		61.2	---	1.200	--	---	1.03	39.30			1978 BM007
		---		61.2	---	1.200	--	---	0.98	38.40			1978 BM007
		---		61.2	---	1.200	--	---	0.78	34.20	38.0/	2.6	1978 BM007
T851	P	3.00	65	64.4	1.500	0.750	CT	0.750	0.55	30.30			1972 83243
		3.00		64.4	1.500	0.750	CT	0.750	0.59	31.40			1972 83243
		3.00		64.4	1.500	0.750	CT	0.750	0.52	29.30	30.3/	1.1	1972 83243
T851	P	3.00	0	63.3	1.500	0.750	CT	0.750	0.63	31.70			1972 83243
		3.00		63.3	1.500	0.750	CT	0.750	0.62	31.40	31.6/	0.2	1972 83243
T851	P	3.00	R.T.	61.0	1.500	0.750	CT	0.750	0.69	32.20			1972 83243
		3.00		61.0	1.500	0.750	CT	0.750	0.67	31.70			1972 83243
		3.00		61.0	1.500	0.750	CT	0.750	0.61	30.00			1972 83243
		1.37		66.1	1.006	0.499	CT	0.513	0.27	21.90			1978 WPC01
		1.37		66.1	1.006	0.499	CT	0.493	0.28	22.90			1978 WPC01
		1.50		67.7	1.000	0.602	CT	0.623	0.38	26.20	27.5/	4.5	1973 86429
T851	P	1.37	86	65.4	1.500	0.500	CT	0.504	0.26	21.30			1973 86213
		1.37		65.8	1.500	0.500	CT	0.484	0.27	21.60			1973 86213
		1.37		65.8	1.500	0.500	CT	0.491	0.23	20.10	21.0/	0.8	1973 86213
T851	P	1.37	88	66.1	1.000	0.499	CT	0.493	0.31	23.40			1973 86213
		1.37		66.1	1.000	0.500	CT	0.513	0.29	22.40	22.9/	0.7	1973 86213
T851	P	3.00	200	56.4	1.500	0.750	CT	0.750	0.70	29.70			1972 83243
		3.00		56.4	1.500	0.750	CT	0.750	0.75	30.90	30.3/	0.8	1972 83243
T851	P	3.00	65	66.8	1.500	0.750	CT	0.750	0.39	26.50			1972 83243

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	THICKNESS (IN)	SPECIMEN		CRACK LENGTH (IN)	2.5* CRACK LENGTH (K(1C)/TVB)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV (IN)	DATE	REFER	
	2024					WIDTH (IN)	THICK (IN)							DESIGN
	M	B												
T851	P	3.00	65	1.500	0.750	CT	0.750	0.43	27.60	26.2/	1.6	1972	83243	
		3.00	L-T	1.500	0.750	CT	0.750	0.33	24.40	26.2/	1.6	1972	83243	
T851	P	3.00	0	1.500	0.750	CT	0.750	0.37	25.20			1972	83243	
		3.00	L-T	1.500	0.750	CT	0.750	0.51	29.50			1972	83243	
T851	P	3.00	R.T.	1.500	0.750	CT	0.750	0.45	27.90	27.5/	2.2	1972	83243	
		3.20	L-T	2.500	1.243	CT	1.206	0.25	18.70			1971	84360	
T851	P	3.20		2.500	1.254	CT	1.226	0.25	18.60			1971	84360	
		2.50		1.970	1.000	CT	1.003	0.40	23.90			1973	86213	
		4.00		2.000	1.020	NB		0.39	24.60			1974	90981	
		4.00		2.000	1.020	NB		0.38	24.40			1974	90981	
		3.00		1.500	0.750	CT	0.750	0.45	26.90			1972	83243	
		3.00		1.500	0.750	CT	0.750	0.47	27.30			1972	83243	
		2.00		2.500	1.251	CT	1.311	0.41	25.70			1971	84360	
		2.00		2.500	1.250	CT	1.303	0.40	25.50			1971	84360	
		2.00		2.500	1.250	CT	1.203	0.30	22.10			1971	84360	
		2.00		2.500	1.250	CT	1.207	0.30	22.30			1971	84360	
		3.00		3.000	1.000	CT	1.239	0.34	23.80			1972	84306	
		3.00		2.490	0.625	CT	1.259	0.26	21.00			1974	90011	
		3.00		2.000	0.750	CT	1.292	0.27	21.30			1972	84306	
		3.00		2.480	0.624	CT	1.292	0.25	20.70			1972	84306	
		3.00		3.000	1.000	CT	1.500	0.26	21.00			1974	90011	
		3.00		3.000	0.755	CT	1.500	0.28	22.00			1974	90011	
		3.00		2.000	0.750	CT	1.500	0.32	23.40			1972	84306	
		3.00		2.000	0.620	CT	1.500	0.34	24.00			1974	90011	
		3.00		2.000	0.620	CT	1.500	0.50	29.00			1974	90011	
		3.00		2.500	0.625	CT	1.232	0.28	21.90			1972	84306	
3.00		2.000	0.750	CT	1.500	0.37	25.00			1974	90011			
3.00		2.000	0.620	CT	1.515	0.50	29.00			1974	90011			
1.75		3.000	0.756	CT	3.035	0.31	22.90			1972	84306			
1.75		3.990	0.499	CT	3.035	0.44	27.30			1972	84306			
3.00		2.300	0.750	CT	3.064	0.60	32.00			1974	90011			
1.75		3.990	0.499	CT	3.064	0.46	27.80			1972	84306			
3.00		2.490	0.624	CT	1.263	0.29	20.40			1972	84306			
1.00		1.987	0.988	CT	1.093	0.32	23.70			1978	MP01			
0.87		1.989	0.877	CT	1.074	0.28	22.50			1978	MP01			
1.37		3.000	1.385	NB	1.480	0.37	25.20			1973	86213			

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	THICKNESS (IN)	SPECIMEN			CRACK LENGTH (IN)	2.5* K(1C)/(TVB)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV (IN)	DATE	REFER		
	FORM	WIDTH (IN)				THICK (IN)	DESIGN	A							B	M
T851	P	1.37	R.T.	L-T	65.6	1.998	1.001	CT	1.059	0.30	23.20		1978	MPC01		
		1.37			65.6	2.980	1.383	NB	1.490	0.27	22.20		1978	MPC01		
		1.37			65.6	1.990	1.001	CT	0.975	0.28	22.50		1978	MPC01		
		1.37			65.6	3.020	1.383	NB	1.480	0.27	21.80		1978	MPC01		
		1.37			65.6	3.000	1.386	NB	1.545	0.31	23.20		1973	86213		
		1.37			65.6	3.000	1.383	NB	1.500	0.31	23.20		1973	86213		
		1.37			65.6	2.000	1.001	CT	1.048	0.30	22.80		1973	86213		
		1.37			65.6	3.000	1.386	NB	1.531	0.33	23.70		1973	86213		
		1.37			65.8	3.020	1.393	NB	1.510	0.36	25.40		1978	MPC01		
		1.37			65.8	2.980	1.393	NB	1.490	0.34	25.00		1978	MPC01		
		3.00			66.0	3.000	0.994	CT	1.540	0.33	24.00		1972	84306		
		3.00			66.0	3.000	0.757	CT	1.526	0.35	24.30		1973	85836		
		3.00			66.0	3.000	0.995	CT	1.533	0.32	23.50		1972	84306		
		1.37			66.1	2.990	1.400	NB	1.525	0.25	21.80		1978	MPC01		
		1.37			66.1	3.000	1.401	NB	1.445	0.25	20.90		1973	86213		
		1.37			66.1	3.000	1.400	NB	1.536	0.28	22.10		1973	86213		
		0.75			66.1	1.502	0.761	CT	0.781	0.27	22.10		1978	MPC01		
		1.00			66.2	3.008	1.401	NB	1.474	0.25	21.50		1978	MPC01		
		0.42			66.2	2.016	1.009	CT	1.149	0.25	21.50		1978	MPC01		
		4.00			66.5	1.508	0.616	CT	0.769	0.25	21.50		1978	MPC01		
		4.00			67.0	2.000	1.020	NB	0.769	0.24	20.40		1974	90981		
		0.75			67.0	1.500	0.709	CT	0.769	0.25	21.00		1974	90981		
		0.50			67.1	1.500	0.709	CT	0.769	0.27	22.00		1982	NC003		
		0.50			67.1	1.506	0.481	CT	0.768	0.24	20.90		1978	MPC01		
0.37			67.1	1.900	0.518	CT	0.765	0.24	21.10		1978	MPC01				
1.50			67.5	1.000	0.375	CT	0.765	0.26	21.90		1974	90981				
1.50			67.5	2.000	1.001	CT	1.018	0.35	25.20		1973	86429				
0.62			68.0	1.980	1.000	CT	1.004	0.33	24.60		1973	86429				
0.75			70.1	1.504	0.631	CT	0.767	0.28	23.60		1978	MPC01				
0.75			70.1	1.500	0.750	CT	0.767	0.29	24.00		1974	90981				
0.75			70.1	1.500	0.750	CT	0.767	0.26	22.80		1974	90981				
0.75			70.1	1.500	0.750	CT	0.767	0.25	22.00	23.3/	2.4	1974	90981			
T851	P	1.37	82	L-T	65.6	2.000	1.002	CT	1.030	0.32	23.40		1973	86213		
		1.37			65.6	2.000	1.001	CT	0.975	0.29	22.50		1973	86213		
		1.37			65.6	2.000	1.002	CT	1.036	0.32	23.40		1973	86213		
		1.37			65.6	2.000	1.001	CT	0.981	0.29	22.40		1973	86213		
1.37			65.6	2.000	1.001	CT	0.982	0.30	22.80		1973	86213				

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM				YIELD STRENGTH (KSI)	SPECIMEN			DESIGN	CRACK LENGTH (IN)	2.5* K(IIC)/TVS)**2 (IN)	K(IIC) MEAN (KBI/SQRT IN)	K(IIC) STAN DEV	DATE	REFER	
	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT		WIDTH (IN)	THICK (IN)	DESIGN								A
T851	P	1.37	82	L-T	65.4	2.000	1.002	CT	1.033	0.32	23.40	23.0/	0.5	1973	86213	
T851	P	1.75	84	L-T	65.0	2.990	1.007	CT	1.650	0.32	23.30			1972	84306	
		1.00			68.9	1.500	0.750	CT	0.726	0.22	20.60			1973	86213	
		1.00			68.9	1.500	0.750	CT	0.739	0.23	20.60			1973	86213	
		1.00			68.9	1.500	0.750	CT	0.742	0.24	21.30	21.5/	1.2	1973	86213	
T851	P	3.00	200	L-T	58.6	1.500	0.750	CT	0.750	0.49	25.90			1972	83243	
		3.00			58.6	1.500	0.750	CT	0.750	0.56	27.80			1972	83243	
		3.00			58.6	1.500	0.750	CT	0.750	0.52	26.80	26.8/	1.0	1972	83243	
T851	P	3.00	300	L-T	54.9	1.500	0.750	CT	0.750	0.60	26.80			1972	83243	
		3.00			54.9	1.500	0.750	CT	0.750	0.62	27.30			1972	83243	
		3.00			54.9	1.500	0.750	CT	0.750	0.59	26.60	26.9/	0.4	1972	83243	
T851	P	1.37	R. T.	T-8	65.4	0.996	0.500	CT	0.488	0.28	22.90			1978	MFC01	
T851	P	1.37	86	T-8	65.4	1.000	0.500	CT	0.510	0.30	22.90			1973	86213	
T851	P	1.37	88	T-8	65.5	1.000	0.500	CT	0.515	0.24	20.40			1973	86213	
		1.37			65.5	1.000	0.500	CT	0.496	0.29	20.60			1973	86213	
		1.37			65.5	1.000	0.500	CT	0.511	0.25	20.80	20.6/	0.2	1973	86213	
T851	P	1.39	- 320	T-L	79.0	3.000	1.390	NB	1.490	0.20	22.10			1971	84288	
		1.39			79.0	3.000	1.390	NB	1.480	0.20	22.20	22.2/	0.1	1971	84288	
T851	P	1.39	- 112	T-L	69.2	3.000	1.390	NB	1.520	0.24	21.30			1971	84288	
		1.39			69.2	3.000	1.390	NB	1.570	0.27	22.70	22.0/	1.0	1971	84288	
T851	P	3.00	- 65	T-L	66.5	1.500	0.750	CT	0.750	0.31	23.30			1972	83243	
T851	P	3.00	0	T-L	65.5	1.500	0.750	CT	0.750	0.30	22.90			1972	83243	
		3.00			65.5	1.500	0.750	CT	0.750	0.25	20.80	21.9/	1.5	1972	83243	
T851	P	4.00	R. T.	T-L	61.5	2.000	1.020	NB	---	0.26	19.80			1974	90981	
		4.00			61.5	2.000	1.020	NB	---	0.26	19.90			1974	90981	
		3.00			63.5	1.500	0.750	CT	0.750	0.32	22.60			1972	83243	
		3.00			63.5	1.500	0.750	CT	0.750	0.24	19.70			1972	83243	
		3.00			63.5	1.500	0.750	CT	0.750	0.31	22.20			1972	83243	

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	ORIENT	TEST TEMP (F)	R. T.	T-L	SPECIMEN DESIGN		CRACK LENGTH (IN)	K(1C)		DATE	REFER
	FORM	THICKNESS (IN)							M	B		(K(1C)/TVB)**2	(K(1C) MEAN DEV (KBI*SQRT IN))		
1851	P	3.00	64.0	2.000	0.750	CT	---	0.32	23.00	23.00	1974	90011			
		3.00	64.0	2.000	0.620	CT	---	0.35	24.00	24.00	1974	90011			
		3.00	64.0	2.490	0.624	CT	1.233	0.20	17.90	17.90	1972	84306			
		3.00	64.0	3.000	1.000	CT	---	0.20	18.00	18.00	1974	90011			
		3.00	64.0	2.500	0.750	CT	---	0.32	23.00	23.00	1974	90011			
		3.00	64.0	2.000	0.620	CT	---	0.32	23.00	23.00	1974	90011			
		3.00	64.0	2.500	0.626	CT	1.222	0.21	18.50	18.50	1972	84306			
		3.00	64.0	2.500	0.750	CT	---	0.38	25.00	25.00	1974	90011			
		3.00	64.0	2.000	0.750	CT	---	0.30	22.00	22.00	1974	90011			
		3.00	64.0	2.000	0.750	CT	---	0.32	23.00	23.00	1974	90011			
		3.00	64.0	2.900	0.623	CT	1.240	0.22	18.60	18.60	1972	84306			
		1.37	64.4	3.020	1.383	NB	1.510	0.21	18.90	18.90	1978	WPC01			
		1.38	64.4	3.000	1.000	NB	0.995	0.23	19.60	19.60	1972	82880			
		1.39	64.4	2.000	1.388	NB	1.507	0.24	20.20	20.20	1971	84288			
		1.39	64.4	3.000	1.380	NB	---	0.25	20.50	20.50	1972	82880			
		1.37	64.4	3.020	1.383	NB	1.510	0.21	19.10	19.10	1978	WPC01			
		1.37	64.4	2.980	1.383	NB	1.520	0.21	19.10	19.10	1978	WPC01			
		1.37	64.4	3.020	1.384	NB	1.540	0.28	22.50	22.50	1978	WPC01			
		1.37	64.4	3.002	1.384	NB	1.501	0.28	22.10	22.10	1978	WPC01			
		1.38	64.4	2.000	1.000	NB	0.986	0.26	20.90	20.90	1972	82880			
		1.39	64.4	3.000	1.387	NB	1.512	0.24	20.10	20.10	1971	84288			
		1.38	64.4	1.500	0.750	NB	0.777	0.30	22.40	22.40	1972	82880			
		1.39	64.4	3.000	1.390	NB	---	0.24	20.20	20.20	1972	82880			
		1.39	64.4	3.000	1.390	NB	---	0.24	20.00	20.00	1972	82880			
		1.39	64.4	3.000	1.395	NB	1.508	0.25	20.50	20.50	1971	84288			
		1.37	64.4	3.021	1.383	NB	1.450	0.17	18.20	18.20	1978	WPC01			
		1.38	64.4	1.000	0.500	NB	0.512	0.27	21.30	21.30	1972	82880			
		1.38	64.4	2.000	1.000	NB	0.503	0.22	19.30	19.30	1972	82880			
		1.38	64.4	2.000	1.000	NB	0.977	0.24	20.00	20.00	1972	82880			
		1.38	64.4	1.000	0.500	NB	0.512	0.26	20.60	20.60	1972	82880			
		4.00	64.6	2.000	1.020	NB	---	0.19	17.60	17.60	1974	90981			
		1.37	64.6	2.000	1.020	NB	---	0.20	18.30	18.30	1974	90981			
		1.37	64.8	2.000	1.000	CT	1.009	0.20	18.30	18.30	1973	86213			
		1.37	64.8	2.000	1.038	CT	1.038	0.23	19.60	19.60	1973	86213			
		1.37	64.8	2.000	1.000	CT	1.055	0.22	19.20	19.20	1973	86213			
		1.37	65.0	3.002	1.392	NB	1.501	0.27	21.60	21.60	1978	WPC01			
		3.00	65.0	2.900	1.246	CT	1.293	0.31	23.00	23.00	1973	85836			
		3.00	65.0	2.900	1.245	CT	1.293	0.31	23.00	23.00	1973	85836			
		1.37	65.0	2.978	1.392	NB	1.489	0.19	18.30	18.30	1978	WPC01			

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM				YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	THICK (IN)	FORM	SPECIMEN		DESIGN	CRACK		2.5* K(IIC)/TVS)**2 (IN)	K(IIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	WIDTH (IN)		THICK (IN)	LENGTH (IN)						LENGTH (IN)	2.5* K(IIC)/TVS)**2 (IN)								
	A	B	B	A						A									
T851	P	1.37	3.024	1.392	65.0	T-L	R.T.	P	1.37	1.512	0.27	22.00	19.80	19.80	19.80	19.80	19.80	1978	MFC01
		1.37	3.000	1.392	65.0				1.37	1.565	0.23	19.80	19.80	19.80	19.80	19.80	19.80	1973	86213
		0.75	1.494	0.761	65.2				1.37	0.792	0.21	20.20	20.20	20.20	20.20	20.20	20.20	1978	MFC01
		1.37	2.000	0.999	65.5				1.37	1.097	0.21	18.20	18.20	18.20	18.20	18.20	18.20	1973	86213
		1.37	2.000	0.999	65.5				1.37	1.065	0.19	18.20	18.20	18.20	18.20	18.20	18.20	1973	86213
		1.37	3.000	1.400	65.5				1.37	1.520	0.23	25.40	25.40	25.40	25.40	25.40	25.40	1978	MFC01
		1.37	2.778	1.385	65.6				1.37	1.489	0.36	21.00	21.00	21.00	21.00	21.00	21.00	1978	MFC01
		1.00	2.016	0.987	65.7				1.00	1.109	0.24	18.90	18.90	18.90	18.90	18.90	18.90	1978	MFC01
		0.62	1.498	0.616	65.7				0.62	0.779	0.19	19.30	19.30	19.30	19.30	19.30	19.30	1978	MFC01
		0.50	1.490	0.481	65.9				0.50	0.760	0.21	22.10	22.10	22.10	22.10	22.10	22.10	1974	70981
		0.37	1.000	0.375	66.6				0.37	---	0.28	32.70	32.70	32.70	32.70	32.70	32.70	1974	70981
		0.37	1.000	0.375	66.6				0.37	---	0.29	23.80	23.80	23.80	23.80	23.80	23.80	1974	70981
		0.50	1.508	0.518	67.2				0.50	0.784	0.32	20.30	20.30	20.30	20.30	20.30	20.30	1978	MFC01
		0.62	1.498	0.631	67.3				0.62	0.794	0.21	21.80	21.80	21.80	21.80	21.80	21.80	1978	MFC01
		0.75	1.500	0.750	68.6				0.75	---	0.25	21.90	21.90	21.90	21.90	21.90	21.90	1974	70981
		0.75	1.500	0.750	68.6				0.75	---	0.25	21.90	21.90	21.90	21.90	21.90	21.90	1974	70981
		0.75	1.500	0.750	68.6				0.75	---	0.26	22.00	22.00	22.00	22.00	22.00	22.00	1974	70981
T851	P	1.37	2.000	1.000	64.4	T-L	82	P	1.37	1.010	0.24	19.90	19.90	19.90	19.90	19.90	19.90	1973	86213
		1.37	2.000	0.999	64.4				1.37	1.021	0.24	20.00	20.00	20.00	20.00	20.00	20.00	1973	86213
		1.37	2.000	1.000	64.4				1.37	0.992	0.24	20.00	20.00	20.00	20.00	20.00	20.00	1973	86213
		1.37	2.000	1.001	64.8				1.37	1.058	0.25	20.40	20.40	20.40	20.40	20.40	20.40	1973	86213
		1.37	2.000	1.002	64.8				1.37	1.032	0.25	20.90	20.90	20.90	20.90	20.90	20.90	1973	86213
		1.37	2.000	1.000	64.8				1.37	1.047	0.24	20.10	20.10	20.10	20.10	20.10	20.10	1973	86213
T851	P	1.00	1.500	0.750	67.6	T-L	84	P	1.00	0.740	0.20	18.90	18.90	18.90	18.90	18.90	18.90	1973	86213
		1.00	1.490	0.749	67.6				1.00	0.754	0.19	18.90	18.90	18.90	18.90	18.90	18.90	1973	86213
		1.00	1.500	0.750	67.6				1.00	0.749	0.18	18.30	18.30	18.30	18.30	18.30	18.30	1973	86213
T851	P	3.00	1.500	0.750	58.3	T-L	200	P	3.00	0.750	0.32	20.70	20.70	20.70	20.70	20.70	20.70	1972	83243
		3.00	1.500	0.750	58.3				3.00	0.750	0.38	22.80	22.80	22.80	22.80	22.80	22.80	1972	83243
		3.00	1.500	0.750	58.3				3.00	0.750	0.35	21.80	21.80	21.80	21.80	21.80	21.80	1972	83243
T851	P	3.00	1.500	0.750	54.1	T-L	300	P	3.00	0.750	0.40	21.70	21.70	21.70	21.70	21.70	21.70	1972	83243
		3.00	1.500	0.750	54.1				3.00	0.750	0.42	22.30	22.30	22.30	22.30	22.30	22.30	1972	83243
T851	P	3.00	2.500	0.750	64.0	8-T	R.T.	P	3.00	---	0.35	24.00	24.00	24.00	24.00	24.00	24.00	1974	90011

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM											K(1C) STAN K(1C) MEAN DEV (KSI#SORT IN)	DATE	REFER	
	---PRODUCT---		TEST SPECIMEN		YIELD STRENGTH		SPECIMEN		CRACK		2.5*				
	FORM	THICK (IN)	TEMP (F)	ORIENT	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)	A	B	(IN)				(IN)
T851	P	1.37	86	S-T	1.000	0.500	CT	0.499	0.19	15.70	1973	86213			
		1.37			1.000	0.500	CT	0.510	0.16	16.00	1973	86213			
		1.37			1.000	0.500	CT	0.511	0.18	17.00	1973	86213			
T851	P	1.37	88	S-T	1.000	0.500	CT	0.502	0.19	15.90	1973	86213			
		1.37			1.000	0.500	CT	0.479	0.15	15.80	1973	86213			
		1.37			1.000	0.500	CT	0.480	0.15	15.80	1973	86213			
T851	P	1.37	88	S-L	1.000	0.501	CT	0.506	0.18	17.20	1973	86213			
		1.37			1.000	0.500	CT	0.476	0.16	16.30	1973	86213			
		1.37			1.000	0.501	CT	0.478	0.15	15.60	1973	86213			
T8510	E	4.50	R.T.	L-T	4.023	2.000	CT	2.132	0.78	33.10	1978	MPC01			
		4.00			3.981	1.838	CT	2.110	0.57	30.20	1978	MPC01			
		2.76			4.018	2.000	CT	2.009	0.46	27.80	1978	MPC01			
T8510	E	4.50	R.T.	T-L	5.042	2.500	CT	2.622	0.21	17.50	1978	MPC01			
		4.00			5.054	2.499	CT	2.527	0.16	16.30	1978	MPC01			
		2.76			4.018	1.999	CT	2.049	0.15	15.60	1978	MPC01			
T8510	E	4.50	R.T.	S-L	3.022	1.500	CT	1.541	0.21	16.50	1978	MPC01			
		4.00			2.998	1.498	CT	1.529	0.19	16.50	1978	MPC01			
		2.76			2.018	0.999	CT	0.989	0.13	14.10	1978	MPC01			
T8511	E	3.50	R.T.	L-T	1.996	1.000	CT	0.978	0.32	24.40	1978	MPC01			
		3.50			2.004	1.000	CT	0.982	0.30	23.80	1978	MPC01			
		3.50	R.T.	T-L	2.015	1.000	CT	1.048	0.19	16.00	1978	MPC01			
T8511	E	3.50	R.T.	T-L	1.980	1.000	CT	1.010	0.15	16.00	1978	MPC01			
		3.50			2.014	1.001	CT	1.007	0.16	16.77	1978	MPC01			
		3.50	R.T.	S-T	2.014	1.001	CT	1.007	0.16	16.77	1978	MPC01			

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEMP (F)	THICK (IN)	SPECIMEN		DESIGN	CRACK LENGTH (IN)	K(1C) (IN)	2.9* K(1C)/(TVB)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV (IN)	DATE	REFER
	2024						K(1C)									
	W	B					A									
T852	F	4.75	84	L-S	84	4.75	2.000	0.997	CT	0.923	0.41	26.20	26.20	1973	86213	
T852	F	5.00	R.T.	L-T	84	5.00	3.000	1.502	NB	1.400	0.54	26.10	26.10	1970	77720	
		5.00				5.00	3.000	1.504	NB	1.542	0.66	28.30	28.30	1970	77720	
		6.00				6.00	4.000	2.001	NB	2.008	0.76	30.80	30.80	1970	77720	
		6.00				6.00	4.000	1.999	NB	1.925	0.63	28.20	28.20	1970	77720	
		6.00				6.00	4.000	2.002	NB	2.202	0.75	30.80	30.80	1970	77720	
		3.00				3.00	2.500	1.254	CT	1.324	0.71	30.90	30.90	1973	89836	
		3.00				3.00	2.490	1.250	CT	1.279	0.55	27.20	27.20	1973	89836	
		3.00				3.00	2.490	1.247	CT	1.251	0.48	25.50	25.50	1973	89836	
		5.00				5.00	2.500	1.252	CT	1.299	0.99	36.90	36.90	1973	89836	
		5.00				5.00	2.500	1.252	CT	1.302	1.02	37.10	37.10	1973	89836	
		5.00				5.00	2.500	1.004	CT	1.265	0.99	37.80	37.80	1973	89836	
		2.00				2.00	1.500	0.752	NB	0.667	0.36	24.30	24.30	1970	77720	
		2.00				2.00	1.500	0.752	NB	0.707	0.30	22.60	22.60	1970	77720	
		2.00				2.00	1.500	0.751	NB	0.770	0.40	25.90	25.90	1970	77720	
		3.00				3.00	2.500	1.250	CT	-----	0.77	36.00	36.00	1974	90011	
		3.00				3.00	2.500	1.250	CT	-----	0.81	37.00	37.00	1974	90011	
		3.00				3.00	2.500	1.250	CT	-----	0.81	37.00	37.00	1974	90011	
		4.00				4.00	3.000	1.500	NB	1.445	0.49	28.90	28.90	1970	77720	
		4.00				4.00	3.000	1.500	NB	1.482	0.36	25.00	25.00	1970	77720	
		4.00				4.00	3.000	1.502	NB	1.445	0.46	28.10	28.10	1970	77720	
		3.00				3.00	2.000	1.000	NB	0.950	0.27	21.90	21.90	1970	77720	
		3.00				3.00	2.000	0.999	NB	0.940	0.29	22.60	22.60	1970	77720	
		3.00				3.00	1.990	1.000	NB	0.935	0.34	24.60	24.60	1970	77720	
T852	F	7.00	82	L-T	82	7.00	1.500	0.751	CT	0.706	0.70	26.20	26.20	1973	86213	
		7.00				7.00	1.490	0.758	CT	0.719	0.28	19.70	19.70	1973	86213	
T852	F	7.00	83	L-T	83	7.00	1.500	0.753	CT	0.720	0.27	19.30	19.30	1973	86213	
T852	F	5.00	84	L-T	84	5.00	1.490	0.750	CT	0.735	0.31	21.80	21.80	1973	86213	
		4.75				4.75	2.000	0.999	CT	1.061	0.34	23.60	23.60	1973	86213	
T852	F	3.00	265	L-T	265	3.00	2.500	1.250	CT	-----	-----	31.00	31.00	1974	90011	
		5.00				5.00	2.490	1.248	CT	1.485	0.90	38.90	38.90	1973	86210	
T852	F	4.75	84	T-S	84	4.75	2.000	0.997	CT	0.937	0.14	15.20	15.20	1973	86213	

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM										K(1C)		DATE	REFER	
	--PRODUCT--		TEST SPECIMEN		YIELD STRENGTH		SPECIMEN		CRACK		2.5*	K(1C) MEAN			STAN
	FORM	THICK (IN)	THICK (IN)	TEMP (F)	ORIENT	STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)					
							M	B	A						
T852	F	5.00	R.T.	T-L	56.7	3.000	1.502	NB	1.507	0.25	17.80	1970	7720		
		5.00			56.7	3.000	1.500	NB	1.422	0.23	17.30	1970	7720		
		5.00			56.7	3.000	1.501	NB	1.553	0.24	17.60	1970	7720		
		6.00			57.8	4.000	2.005	NB	2.005	0.17	15.10	1970	7720		
		6.00			57.8	3.990	2.003	NB	2.039	0.25	18.10	1970	7720		
		6.00			57.8	3.990	2.003	NB	2.035	0.25	18.20	1973	86213		
		6.00			57.8	4.000	2.005	NB	2.005	0.17	15.20	1973	86213		
		3.00			58.0	2.000	1.000	CT	----	0.30	20.00	1974	90011		
		3.00			58.0	2.000	1.000	CT	----	0.33	21.00	1974	90011		
		3.00			58.0	2.000	1.000	CT	----	0.33	21.00	1974	90011		
		2.00			63.8	1.500	0.754	NB	0.697	0.34	23.50	1970	7720		
		2.00			63.8	1.500	0.752	NB	0.667	0.36	24.10	1970	7720		
		2.00			63.8	1.500	0.749	NB	0.763	0.24	19.80	1970	7720		
		3.00			69.0	2.000	1.001	NB	1.020	0.15	16.90	1970	7720		
		3.00			69.0	1.990	1.000	NB	1.010	0.15	16.70	1970	7720		
		3.00			69.0	2.000	1.000	NB	0.905	0.20	19.40	18.9/	2.6		
T852	F	7.00	82	T-L	59.0	1.500	0.750	CT	0.719	0.47	25.50	1973	86213		
T852	F	7.00	83	T-L	53.2	1.500	0.754	CT	0.757	0.39	21.00	1973	86213		
T852	F	7.00			59.5	1.500	0.753	CT	0.767	0.21	17.20	19.1/	2.7		
T852	F	5.00	84	T-L	62.9	1.490	0.750	CT	0.752	0.19	15.40	1973	86213		
T852	F	3.00	269	T-L	----	2.500	1.250	CT	----	----	24.00	1974	90011		
T852	F	6.00	R.T.	S-T	53.9	1.400	0.700	NB	0.700	0.27	17.70	1972	82675		
T852	F	6.00			53.9	1.400	0.700	NB	0.700	0.26	17.50	17.6/	0.1		
T852	F	7.00	83	S-T	50.1	1.000	0.506	CT	0.495	0.40	20.00	1973	86213		
		7.00			50.5	1.000	0.499	CT	0.481	0.32	18.00	1973	86213		
		7.00			57.2	1.000	0.505	CT	0.494	0.23	17.40	18.5/	1.4		
T852	F	5.00	84	S-T	57.6	0.990	0.501	CT	0.542	0.23	17.60	1973	86213		
T852	F	6.00	R.T.	S-L	53.9	1.000	0.500	NB	0.512	0.23	16.40	1970	7720		
		6.00			53.9	1.000	0.500	NB	0.505	0.19	14.80	1970	7720		
		6.00			53.9	1.000	0.500	NB	0.507	0.26	17.30	1970	7720		
		5.00			54.5	1.000	0.500	NB	0.490	0.22	16.00	1970	7720		

TABLE 7.5.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	THICK (IN)	SPECIMEN		CRACK LENGTH (IN)	2.9* (K(1C)/TV8)**2 (1-1)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER		
	FORM	2024				WIDTH (IN)	THICK (IN)							DESIGN	K(1C)
T852	F	5.00	54.5	R. T.	5.00	0.500	NB	0.473	0.21	15.80		1970	77720		
		4.00	60.6		0.500	0.250	NB	0.267	0.15	15.00		1970	77720		
		4.00	60.6		0.500	0.250	NB	0.272	0.17	15.80		1970	77720		
T852	F	4.75	60.9	84	S-L	2.000	0.997	CT	0.946	0.17	16.10	1973	86213		

TABLE 7.5.2.2

ALUMINUM		2024		K(C)		CRACK LENGTH GROSS STRESS									
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	---SPECIMEN---		INIT FINAL ONSET		MAX		K (APP) STAN		K (C) STAN		K(C) STAN MEAN DEV DATE REFER	
				WIDTH (IN)	THICK (IN)	(IN)	(IN)	(KBI)	(KBI)	(KSI*SQRT IN)	(KSI*SQRT IN)	MEAN DEV (IN)	MEAN DEV (IN)		
	H	B		2A(O)	2A(F)	S(O)	S(MAX)								
BUCKLING OF CRACK EDGES RESTRAINED															
T3	S	0.03	R. T.	L-T	52.0	20.000	0.032	0.640	1.200	47.60	48.50	48.66*	66.74*	1966 67821	
		0.03			52.0	20.000	0.032	1.120	2.060	43.10	47.00	62.46*	85.10*	1966 67821	
		0.03			52.0	20.000	0.032	7.460	9.300	16.30	22.40	84.00	100.98*	1966 67821	
		0.03			52.0	20.000	0.032	3.260	7.070	20.00	27.60	82.90	99.78*	1966 67821	
		0.03			52.0	20.000	0.032	3.450	4.860	22.80	36.40	86.33*	83.5/ 0.8 104.40*	1966 67821	
T3	S	0.04	R. T.	L-T	50.6	6.450	0.040	2.820	---	---	26.30	62.95*	---	1966 86734	
		0.04			50.6	6.450	0.040	2.650	---	---	26.70	60.95*	---	1966 86734	
		0.04			50.6	6.450	0.040	3.900	---	---	16.90	54.84*	---	1966 86734	
T3	S	0.04	R. T.	L-T	51.7	9.700	0.040	3.980	---	---	28.60	79.98*	---	1966 86734	
T3	S	0.05	R. T.	L-T	52.7	8.000	0.049	4.770	5.750	17.10	17.20	68.27*	88.25*	1970 78982	
		0.05			52.7	8.000	0.091	2.660	3.600	19.10	31.30	68.73*	85.36*	1970 78982	
T3	S	0.05	R. T.	L-T	52.7	24.000	0.049	7.000	13.300	17.00	27.60	96.64	159.57*	1970 78982	
		0.05			52.7	24.000	0.049	7.160	11.000	16.20	28.30	100.48	135.67*	1970 78982	
		0.05			52.7	24.000	0.049	14.270	18.000	12.70	16.50	101.30	141.83*	1970 78982	
		0.05			52.7	24.000	0.049	2.320	7.400	34.00	42.20	81.03*	99.5/ 2.5 132.94*	1970 78982	
T3	S	0.06	R. T.	L-T	51.9	12.000	0.063	4.720	9.420	24.40	27.70	83.54*	92.79*	1966 67821	
		0.06			51.9	12.000	0.063	3.080	3.810	23.30	33.20	76.14*	86.67*	1966 67821	
T3	S	0.06	R. T.	L-T	51.9	20.000	0.063	4.310	7.770	26.70	30.60	81.98	118.90*	1966 67821	
		0.06			51.9	20.000	0.063	0.870	2.200	43.60	43.60	51.03*	81.66*	1966 67821	
		0.06			51.9	20.000	0.063	7.200	13.300	23.20	23.20	84.91	132.84*	1966 67821	
		0.06			51.9	20.000	0.063	0.960	2.600	38.50	43.60	53.62*	89.04*	1966 67821	
		0.06			51.9	20.000	0.063	3.270	5.030	19.20	37.70	86.88*	110.30*	1966 67821	
		0.06			51.9	20.000	0.063	4.930	6.900	25.60	32.20	93.12*	83.4/ 2.1 114.53*	1966 67821	
T3	S	0.06	R. T.	L-T	51.9	30.000	0.063	7.130	10.710	19.80	26.40	91.56	117.67	1966 67821	
		0.06			51.9	30.000	0.063	5.730	8.090	22.00	28.80	88.40	107.53	1966 67821	
		0.06			51.9	30.000	0.063	3.670	6.710	27.50	39.70	96.21*	133.01*	1966 67821	
		0.06			51.9	30.000	0.063	10.860	14.400	17.60	18.20	81.89	87.3/ 4.9 101.38 108.9/ 8.2 1966 67821		

*NOTE- NET SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)							
CONDITION	--PRODUCT-- FORM THICK TEMP OR (IN) (F)	TEST SPEC YIELD OR STR (KSI)	---SPECIMEN---		CRACK LENGTH CROSS STRESS		K(A) STAN K(A)PP) MEAN DEV (KSI*SQRT IN)	K(C) STAN K(C) MEAN DEV (KSI*SQRT IN)	REFER DATE		
			WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)				ONSET (KSI)	MAX (KSI)
T3	S	53.3	20.000	0.080	7.350	8.950	20.80	24.80	92.09	106.46*	1966 67821
		53.3	20.000	0.080	5.090	6.450	21.30	29.00	85.44	98.71*	1966 67821
		53.3	20.000	0.080	3.310	4.950	29.20	34.20	79.33	99.14*	1966 67821
		53.3	20.000	0.080	1.270	1.900	46.46	48.00	67.96*	83.39*	1966 67821
		53.3	20.000	0.080	0.700	1.440	51.90	51.80	54.36*	78.16*	1966 67821
T3	S	53.8	4.000	0.122	2.390	3.100	---	20.30	51.17*	76.14*	1970 78982
		53.8	4.000	0.123	1.190	1.800	---	35.20	50.93*	67.88*	1970 78982
		53.8	4.000	0.123	2.340	2.900	---	20.50	50.46*	67.62*	1970 78982
		53.8	4.000	0.123	0.390	1.000	---	46.00	36.22*	59.98*	1970 78982
		53.8	4.000	0.123	2.400	---	---	44.90	113.71*	---	1970 78982
		53.8	4.000	0.123	1.200	1.900	---	36.60	53.23*	73.79*	1970 78982
T3	S	53.8	8.000	0.123	0.800	1.900	---	46.40	52.34*	83.07*	1970 78982
		53.8	8.000	0.124	2.600	3.300	---	34.30	74.21*	87.46*	1970 78982
		53.8	8.000	0.123	4.700	4.900	---	20.50	71.70*	75.21*	1970 78982
		53.8	8.000	0.123	4.740	5.260	---	19.60	69.20*	78.70*	1970 78982
		53.8	8.000	0.123	0.800	2.000	---	46.40	52.34*	85.56*	1970 78982
T3	S	53.8	24.000	0.123	14.350	16.200	---	15.40	95.15	111.14*	1970 78982
		53.8	24.000	0.123	14.390	17.800	---	13.10	81.20	110.25*	1970 78982
		53.8	24.000	0.123	2.400	3.250	---	44.60	87.13*	101.93*	1970 78982
		53.8	24.000	0.123	2.400	4.400	---	44.60	87.13*	119.74*	1970 78982
		53.8	24.000	0.123	7.650	11.600	---	29.20	108.07	146.35*	1970 78982
		53.8	24.000	0.123	6.220	11.800	---	28.00	91.33	93.97/11.1	142.43*
T3	S	43.4	6.000	0.060	2.000	2.350	---	30.25	57.62*	64.31*	1966 86734
T3	S	43.4	9.000	0.060	3.000	3.600	---	30.50	71.15*	80.64*	1966 86734
T3	S	43.4	15.000	0.060	5.000	5.800	---	28.00	84.32*	93.27*	1966 86734
T3	S	43.4	18.000	0.060	6.000	7.200	---	27.50	90.72*	102.82*	1966 86734
T3	S	43.4	21.000	0.060	7.000	8.600	---	27.40	97.63*	112.58*	1966 86734

BUCKLING OF CRACK EDGES RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)									
CONDITION	---PRODUCT--- FORM THICK TEMP OR (IN) (F)	TEST SPEC STR (KSI)	CRACK LENGTH GROSS STRESS				K(C) STAN MEAN DEV (KBI*SQRT IN)	K(C) STAN MEAN DEV (KBI*SQRT IN)					
			WIDTH (IN)	THICK (IN)	INIT 2A(D)	FINAL 2A(F)			ONSET S(O)	MAX S(MAX)			
T3	S 0.06 R.T. T-L	43.4	24.000	0.060	8.000	9.600	---	26.70	101.71*	115.27*	1966	86734	
T3	S 0.08 R.T. T-L	46.8	48.000	0.080	24.000	28.420	---	18.30	133.62	138.14*	1962	62308	
	0.08	46.8	48.010	0.080	24.000	28.390	---	18.60	135.80	134.7 / 1.5	160.52*	---	1962 62308
BUCKLING OF CRACK EDGES RESTRAINED													
T3	S 0.06 R.T. L-T	50.0	2.000	0.063	0.626	0.920	32.40	36.20	38.23*	50.25*	1973	86213	
	0.06	50.0	2.000	0.063	0.624	0.870	30.10	36.20	38.16*	48.06*	1973	86213	
	0.06	50.0	2.000	0.063	0.626	0.900	---	34.30	38.34*	49.50*	1973	86213	
	0.06	53.2	2.000	0.064	0.621	1.000	---	36.10	37.90*	53.80*	1973	86213	
	0.06	53.5	2.000	0.061	0.621	0.800	---	39.30	41.26*	48.98*	1973	86213	
	0.06	53.5	2.000	0.061	0.624	1.030	35.90	38.90	41.00*	59.56*	1973	86213	
	0.06	53.5	2.000	0.061	0.622	0.960	35.40	38.80	40.81*	55.80*	1973	86213	
T3	S 0.06 R.T. L-T	51.6	15.800	0.062	3.990	6.080	---	32.20	83.94*	109.70*	1973	86213	
	0.06	51.6	15.810	0.063	6.010	7.080	---	24.20	81.77	92.41*	1973	86213	
	0.06	51.6	15.810	0.063	3.010	4.260	---	37.10	82.52*	100.51*	1973	86213	
	0.06	51.6	15.820	0.062	1.010	1.440	---	49.80	62.88*	75.28*	1973	86213	
T3	S 0.08 R.T. L-T	52.7	12.000	0.081	4.820	---	---	27.90	85.43*	---	1956	84367	
	0.08	52.7	12.000	0.081	1.280	---	---	50.90	72.69*	---	1956	84367	
	0.08	52.7	12.000	0.081	2.430	---	---	43.20	86.60*	---	1956	84367	
	0.08	52.7	12.000	0.081	1.330	---	---	51.70	75.30*	---	1956	84367	
	0.08	52.7	12.000	0.081	2.960	---	---	41.40	92.77*	---	1956	84367	
	0.08	52.7	12.000	0.081	2.910	---	---	43.10	55.64*	---	1956	84367	
	0.08	52.7	12.000	0.081	2.980	---	---	44.30	79.66*	---	1956	84367	
	0.08	52.7	12.000	0.081	4.830	---	---	28.80	88.32*	---	1956	84367	
	0.08	52.7	12.000	0.081	3.180	---	---	39.70	92.78*	---	1956	84367	
	0.08	52.7	12.000	0.081	4.740	---	---	24.80	81.07*	---	1956	84367	
	0.08	52.7	12.000	0.081	4.950	---	---	17.60	86.19*	---	1956	84367	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

CONDITION	PRODUCT FORM	THICK (IN)	TEST TEMP (F)	SPEC OR STR (KSI)	YIELD STR (KSI)	SPECIMEN				CRACK LENGTH				GROSS STRESS				K(C) STAN DEV (KSI*SQRT IN)	K(C) MEAN (KSI*SQRT IN)	STAN DEV (KSI*SQRT IN)	REFER DATE					
						W	B	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (IN)	MAX (IN)	K (KSI)	K (KSI)	K (KSI)	K (KSI)	K (KSI)					K (KSI)	K (KSI)			
																								2A(F)	2A(F)	S(O)
T3	S	0.09	R.T.	L-T	51.1	3.000	0.092	1.210	2.002	---	30.30	46.53*	76.06*	1973	86213											
																51.1	3.000	0.092	1.190	1.992	---	30.50	46.27*	76.02*	1973	86213
																51.1	3.000	0.092	1.240	2.215	---	29.90	46.76*	88.16*	1973	86213
T3	S	0.12	R.T.	L-T	53.7	3.000	0.124	1.143	2.080	17.10	32.40	47.73*	86.04*	1973	86213											
																53.7	3.000	0.124	1.223	2.040	17.40	31.20	48.26*	80.47*	1973	86213
																53.7	3.000	0.124	1.123	1.940	19.90	33.30	48.46*	80.08*	1973	86213
																53.8	3.000	0.125	1.167	1.830	16.30	32.30	48.29*	72.22*	1973	86213
																53.8	3.000	0.127	1.140	1.760	15.70	33.10	48.70*	70.78*	1973	86213
																53.8	3.000	0.126	1.190	1.790	15.00	31.60	47.94*	68.87*	1973	86213
																53.8	3.000	0.129	1.165	1.780	16.70	32.30	48.23*	69.93*	1973	86213
																53.8	3.000	0.130	1.257	1.840	15.10	29.70	46.89*	66.84*	1973	86213
																53.8	3.000	0.130	1.150	1.800	17.80	32.50	48.12*	71.28*	1973	86213
																56.0	4.000	0.125	1.645	2.749	---	31.40	56.46*	94.95*	1973	86213
																56.9	4.000	0.125	1.627	2.678	---	31.50	56.18*	91.72*	1973	86213
																T3	S	0.16	R.T.	L-T	50.4	3.000	0.160	1.140	1.780	15.90
50.4	3.000	0.161	1.163	1.820	16.90	30.40	45.34*	67.53*	1973	86213																
50.4	3.000	0.162	1.162	1.890	17.80	30.50	45.49*	69.08*	1973	86213																
50.6	3.000	0.163	1.163	1.780	17.70	30.50	45.49*	66.05*	1973	86213																
50.6	3.000	0.163	1.255	1.710	15.70	28.70	45.26*	59.49*	1973	86213																
50.6	3.000	0.163	1.190	1.760	17.20	31.20	46.19*	66.72*	1973	86213																
53.8	3.000	0.163	1.140	1.840	16.60	32.80	48.26*	73.81*	1973	86213																
53.8	3.000	0.163	1.162	1.810	16.10	32.10	47.88*	70.85*	1973	86213																
53.8	3.000	0.164	1.127	1.800	17.10	33.10	48.28*	72.60*	1973	86213																
50.8	29.990	0.163	15.000	18.360	---	20.70	119.51*	146.96*	1962	62308																
50.8	30.010	0.163	15.000	18.880	---	20.60	118.90*	151.24*	1962	62308																
T3	P	0.25	R.T.	L-T	53.6	15.000	0.255	7.500	11.440	---	21.50	87.76*	1966	86734												
															53.6	15.000	0.253	7.500	11.250	---	21.30	86.94	144.74*	1966	86734	
T3	P	0.50	R.T.	L-T	54.8	7.960	0.509	4.820	5.000	12.80	18.00	64.99*	1970	78982												
															54.8	8.000	0.500	2.600	2.770	21.00	30.60	66.20*	69.00*	1970	78982	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

CONDITION	ALUMINUM	2024	K(C)	CRACK LENGTH CROSS STRESS										K(C) STAN MEAN DEV (KSI*SQRT IN)	K(C) STAN MEAN DEV (KSI*SQRT IN)	REFER
				SPECIMEN		INIT		FINAL		ONSET		MAX				
				W	B	(IN)	(IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI)	(KSI)			
T3	P	0.50	R. T.	L-T	54.8	8.050	0.509	4.850	4.900	13.20	18.00	64.98*	65.76*	1970	78982	
T3	P	0.50	R. T.	L-T	55.4	15.000	0.517	7.500	10.080	---	18.70	76.33	106.01*	1966	86734	
T3	P	0.50	R. T.	L-T	55.4	15.000	0.515	7.500	10.420	---	18.70	76.33	76.3/ 0.0	111.37*	1966	86734
T3	P	0.50	R. T.	L-T	54.8	24.000	0.509	7.250	12.000	17.20	26.80	95.89	138.37*	1970	78982	
T3	P	0.50	R. T.	L-T	54.8	24.150	0.509	7.200	11.500	18.50	27.60	98.26	137.01*	1970	78982	
T3	P	0.50	R. T.	L-T	54.8	24.150	0.509	14.100	17.400	---	15.50	93.54	124.29*	1970	78982	
T3	P	0.50	R. T.	L-T	54.8	24.150	0.509	2.300	4.800	25.70	42.80	81.81*	95.9/ 2.4	120.47*	1970	78982
T3	S	0.06	R. T.	T-L	44.4	2.000	0.064	0.625	1.080	32.30	33.20	34.99*	53.17*	1973	86213	
T3	S	0.06	R. T.	T-L	44.4	2.000	0.063	0.626	1.030	28.30	34.10	36.01*	52.21*	1973	86213	
T3	S	0.06	R. T.	T-L	46.2	2.000	0.064	0.620	0.980	---	33.90	35.59*	49.63*	1973	86213	
T3	S	0.06	R. T.	T-L	47.8	2.000	0.061	0.623	0.900	---	35.40	37.24*	48.27*	1973	86213	
T3	S	0.06	R. T.	T-L	47.8	2.000	0.061	0.621	1.040	34.40	35.20	36.95*	54.38*	1973	86213	
T3	S	0.06	R. T.	T-L	47.8	2.000	0.062	0.625	1.050	28.00	34.70	36.57*	54.09*	1973	86213	
T3	B	0.06	R. T.	T-L	46.0	15.810	0.064	6.010	---	---	22.50	76.02	---	1973	86213	
T3	B	0.06	R. T.	T-L	46.0	15.810	0.063	4.000	---	---	29.10	75.96*	---	1973	86213	
T3	B	0.06	R. T.	T-L	46.0	15.810	0.064	3.010	4.110	---	32.80	72.76*	86.99*	1973	86213	
T3	B	0.06	R. T.	T-L	46.0	15.820	0.064	1.020	1.780	---	43.00	54.57*	72.47*	1973	86213	
T3	B	0.06	R. T.	T-L	44.0	24.000	0.063	8.000	9.600	---	27.80	105.90*	120.02*	1966	86734	
T3	B	0.06	R. T.	T-L	44.0	24.000	0.063	8.000	9.600	---	28.40	108.18*	122.61*	1966	86734	
T3	B	0.06	R. T.	T-L	44.0	24.000	0.063	8.000	9.600	---	27.20	103.61*	117.43*	1966	86734	
T3	B	0.06	R. T.	T-L	44.0	24.000	0.063	8.000	9.600	---	27.90	106.28*	120.45*	1966	86734	
T3	S	0.09	R. T.	T-L	45.3	3.000	0.093	1.190	2.480	---	28.70	43.54*	109.23*	1973	86213	
T3	S	0.09	R. T.	T-L	45.3	3.000	0.093	1.200	2.336	---	28.60	43.66*	93.86*	1973	86213	
T3	S	0.09	R. T.	T-L	45.3	3.000	0.092	1.220	2.372	---	28.00	43.26*	95.11*	1973	86213	
T3	S	0.12	R. T.	T-L	45.7	3.000	0.124	1.130	2.250	15.20	30.50	44.60*	92.69*	1973	86213	
T3	S	0.12	R. T.	T-L	45.7	3.000	0.124	1.178	---	16.60	29.30	44.13*	---	1973	86213	
T3	S	0.12	R. T.	T-L	45.7	3.000	0.124	1.148	---	16.90	29.80	44.06*	---	1973	86213	
T3	S	0.12	R. T.	T-L	46.0	3.000	0.127	1.180	2.250	14.80	28.50	42.98*	86.61*	1973	86213	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

CONDITION	ALUMINUM		CRACK LENGTH CROSS STRESS										K(C)		K(C)		K(C)		STAN DEV DATE REFER	
	--PRODUCT-- FORM (IN)	TEST THICK TEMP (F)	--SPECIMEN--		INIT		FINAL		ONSET		MAX		K(APP)		STAN		K(C)			
			WIDTH (IN)	THICK (IN)	(IN)	(IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI)	(KSI)	MEAN	DEV	(KSI)	MEAN	DEV			
			B	2A(D)	2A(F)	S(D)	S(MAX)													
BUCKLING OF CRACK EDGES NOT RESTRAINED																				
T3	S	0.12	R.T.	T-L	46.0	3.000	0.127	1.233	2.200	13.70	27.70	43.11*	80.74*	1973	86213					
		0.12			46.0	3.000	0.128	1.137	2.160	15.00	29.50	43.30*	83.28*	1973	86213					
		0.12			48.1	3.000	0.129	1.110	2.190	17.10	30.10	43.47*	87.03*	1973	86213					
		0.12			48.1	3.000	0.129	1.107	2.110	16.90	30.10	43.37*	81.75*	1973	86213					
T3	S	0.16	R.T.	T-L	43.2	3.000	0.161	1.183	2.110	14.70	27.50	41.52*	74.69*	1973	86213					
		0.16			43.2	3.000	0.161	1.260	2.120	15.50	26.00	41.15*	71.15*	1973	86213					
		0.16			43.2	3.000	0.162	1.160	2.050	15.20	27.40	40.82*	71.18*	1973	86213					
		0.16			43.5	3.000	0.162	1.137	2.090	14.40	28.10	41.24*	75.18*	1973	86213					
		0.16			43.5	3.000	0.162	1.202	2.110	15.90	27.00	41.26*	73.33*	1973	86213					
		0.16			43.5	3.000	0.162	1.242	2.070	14.20	26.10	40.86*	68.80*	1973	86213					
		0.16			43.6	3.000	0.162	1.259	2.240	15.60	27.70	43.68*	83.47*	1973	86213					
		0.16			43.6	3.000	0.162	1.117	2.110	16.90	30.30	43.93*	82.29*	1973	86213					
		0.16			43.6	3.000	0.162	1.130	2.160	15.70	30.20	44.16*	85.23*	1973	86213					
T3	S	0.16	R.T.	T-L	43.4	30.000	0.164	13.000	18.900	---	18.20	103.06*	133.83*	1966	86734					
		0.16			43.4	30.000	0.165	13.000	18.430	---	18.20	103.06*	129.94*	1966	86734					
T3	S	0.09	84	T-L	44.3	16.000	0.095	4.000	6.420	18.10	29.80	77.71*	105.29*	1973	86213					
		0.09			44.3	16.000	0.095	4.000	6.530	15.80	27.30	76.41*	104.82*	1973	86213					
T3	P	0.25	R.T.	T-L	47.3	15.000	0.255	7.500	9.950	---	19.40	79.19*	107.98*	1966	86734					
		0.25			47.3	15.000	0.254	7.500	9.650	---	19.30	78.78*	103.08*	1966	86734					
T3	P	0.50	R.T.	T-L	49.2	15.000	0.519	7.500	10.400	---	16.20	66.12	96.20*	1966	86734					
		0.50			49.2	15.000	0.516	7.500	10.350	---	15.70	64.08	92.54*	1966	86734					
BUCKLING OF CRACK EDGES NOT RESTRAINED																				
T351	P	0.25	R.T.	L-T	55.4	4.000	0.246	1.733	2.627	---	29.00	54.25*	82.17*	1973	86213					
		0.25			55.8	4.000	0.247	1.727	2.706	---	29.80	55.60*	88.08*	1973	86213					
T351	P	0.50	R.T.	L-T	49.0	4.000	0.498	1.789	---	---	28.00	53.70*	---	1966	86734					

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD DEV

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)		CRACK LENGTH CROSS STRESS						K(C) STAN		
CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	---SPECIMEN---			MAX			K(APP) STAN		K(C) STAN	
					WIDTH (IN)	THICK (IN)	INIT 2A(D)	FINAL 2A(F)	ORIBET R(D)	(KSI) S(MAX)	(KSI) SORT	MEAN (KSI)	DEV (IN)	MEAN (KSI)
BUCKLING OF CRACK EDGES NOT RESTRAINED														
T351	P	0.50	R. T.	L-T	49.0	4.000	0.503	1.880	---	28.00	59.95*	---	---	1966 86734
		0.50			54.0	4.000	0.507	1.673	---	15.80	30.30	55.17*	---	1973 86213
		0.50			54.3	4.000	0.508	1.653	---	15.70	30.70	55.40*	---	1973 86213
T351	P	0.50	R. T.	L-T	49.0	12.000	0.441	7.750	---	18.00	86.42*	---	---	1966 86734
		0.50			49.0	12.000	0.444	5.000	---	29.10	91.56*	---	---	1966 86734
		0.50			49.0	12.000	0.448	9.620	---	9.00	63.19*	---	---	1966 86734
T351	P	1.00	R. T.	L-T	58.2	20.000	1.023	4.850	7.550	28.00	80.21	105.89	---	1973 86213
		1.00			58.2	20.000	1.023	2.610	6.250	35.60	72.85	118.78*	---	1973 86213
		1.00			58.2	20.000	1.023	7.000	10.000	23.00	82.59	78.6/ 3.1	106.40 107.1/ 1.8	1973 86213
T351	P	0.25	R. T.	T-L	47.1	4.000	0.255	1.790	2.900	23.80	49.69*	63.28*	---	1973 86213
		0.25			47.1	4.000	0.255	1.860	2.240	22.90	45.35*	53.80*	---	1973 86213
T351	P	0.50	R. T.	T-L	48.6	14.970	0.507	4.970	7.900	23.80	71.41	102.00*	---	1973 86213
		0.50			48.6	15.000	0.507	5.000	8.600	23.50	70.77	71.1/ 0.5	109.59*	1973 86213
T351	P	1.00	R. T.	T-L	52.0	20.000	1.023	4.850	8.500	24.00	68.75	98.96*	---	1973 86213
		1.00			52.0	20.000	1.023	7.000	10.100	19.90	71.46	94.63	---	1973 86213
		1.00			52.0	20.000	1.023	2.610	6.430	30.90	63.23	67.8/ 4.2	105.18*	1973 86213
BUCKLING OF CRACK EDGES NOT RESTRAINED														
T36	S	0.06	R. T.	L-T	63.6	2.000	0.062	0.625	1.160	41.30	43.33*	71.21*	---	1973 86213
		0.06			63.6	2.000	0.062	0.625	1.250	41.90	44.16*	78.77*	---	1973 86213
T36	S	0.06	R. T.	T-L	56.4	2.000	0.062	0.625	1.280	37.40	39.42*	72.43*	---	1973 86213
		0.06			56.4	2.000	0.062	0.625	1.220	37.50	39.53*	68.46*	---	1973 86213

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD DEV

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)		CRACK LENGTH GROSS STRESS						K(C)		K(C)		K(C)		K(C)			
CONDITION	FORM	THICK (IN)	TEST SPEC YIELD STR (KSI)	THICK (IN)	SPECIMEN W	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI)	K(APP) (KSI)	STAN DEV (KSI)	STAN DEV (KSI)	K(C) (KSI)	K(C) (KSI)	STAN DEV (KSI)	STAN DEV (KSI)	REFER DATE	REFER	
																					2A(D)
BUCKLING OF CRACK EDGES NOT RESTRAINED																					
T4	S	0.04	R.T.	L-T	7.500	0.040	1.930	---	---	27.40	50.06*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	1.930	---	---	29.00	52.66*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	0.500	---	---	40.30	35.81*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	1.100	---	---	39.60	47.43*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	0.500	---	---	40.50	35.99*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	4.100	---	---	16.83	52.84*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	0.540	---	---	39.60	36.59*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	5.000	---	---	12.14	48.11*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	4.600	---	---	12.13	43.16*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	1.000	---	---	36.30	46.00*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	0.500	---	---	39.20	34.84*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	3.860	---	---	17.47	51.76*	---	---	---	---	---	---	---	---	1966 86734	
T4	S	0.06	R.T.	L-T	7.500	0.064	1.500	---	---	34.90	54.93*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	1.020	---	---	37.60	48.14*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	0.500	---	---	42.00	37.32*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	0.800	---	---	40.00	45.16*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	1.000	---	---	37.70	47.77*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	2.100	---	---	30.70	58.62*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	0.500	---	---	41.20	36.61*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	4.030	---	---	17.80	54.94*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	5.000	---	---	12.13	48.08*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	0.500	---	---	42.30	37.59*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	3.100	---	---	12.13	29.99*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			7.500	0.064	3.900	---	---	18.50	55.34*	---	---	---	---	---	---	---	---	1966 86734	
T4	S	0.04	R.T.	T-L	7.500	0.040	0.550	---	---	38.10	35.53*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	4.020	---	---	14.87	45.79*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	0.500	---	---	38.90	34.57*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	0.500	---	---	39.30	34.92*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	2.020	---	---	27.70	51.67*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	1.030	---	---	35.90	46.15*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	0.530	---	---	38.10	34.87*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	1.100	---	---	34.20	45.56*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			7.500	0.040	2.060	---	---	27.30	51.53*	---	---	---	---	---	---	---	---	1966 86734	

*NOTE- NET SECTION STRESS EXCEEDS BOX OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

CONDITION	ALUMINUM		2024		K(C)		CRACK LENGTH CROSS STRESS						K(C) STAN		K(C) STAN							
	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR	YIELD (KSI)	---SPECIMEN---		INIT		FINAL		ONSET		MAX		K (APP) MEAN	STAN DEV	K (C) (KSI*SQRT IN)	MEAN	DEV	DATE	REFER	
					WIDTH (IN)	THICK (IN)	W	B	2A(O)	2A(F)	S(O)	S(MAX)	K (C) (KSI*SQRT IN)	STAN DEV								
T4	S	0.04	R. T.	T-L	37.7	7.500	0.040	5.350	---	---	12.13	53.30*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			37.7	7.500	0.040	4.000	---	---	16.00	49.03*	---	---	---	---	---	---	---	---	1966 86734	
		0.04			37.7	7.500	0.040	5.000	---	---	12.14	48.11*	---	---	---	---	---	---	---	---	1966 86734	
T4	S	0.06	R. T.	T-L	41.4	7.500	0.064	2.080	---	---	28.00	53.15*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			41.4	7.500	0.064	1.100	---	---	35.20	46.87*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			41.4	7.500	0.064	4.300	---	---	14.63	48.24*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			41.4	7.500	0.064	0.310	---	---	37.90	34.02*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			41.4	7.500	0.064	0.500	---	---	39.40	35.01*	---	---	---	---	---	---	---	---	1966 86734	
		0.06			41.4	7.500	0.064	1.960	---	---	29.70	54.42*	---	---	---	---	---	---	---	---	---	1966 86734
		0.06			41.4	7.500	0.064	3.900	---	---	17.58	52.59*	---	---	---	---	---	---	---	---	---	1966 86734
		0.06			41.4	7.500	0.064	0.500	---	---	40.80	36.26*	---	---	---	---	---	---	---	---	---	1966 86734
		0.06			41.4	7.500	0.064	5.200	---	---	11.54	48.43*	---	---	---	---	---	---	---	---	---	1966 86734
		0.06			41.4	7.500	0.064	0.560	---	---	38.80	36.52*	---	---	---	---	---	---	---	---	---	1966 86734
	0.06			41.4	7.500	0.064	4.100	---	---	16.00	50.23*	---	---	---	---	---	---	---	---	---	1966 86734	
	0.06			41.4	7.500	0.064	1.150	---	---	34.70	47.33*	---	---	---	---	---	---	---	---	---	1966 86734	
T6	S	0.06	R. T.	L-T	54.7	2.000	0.062	0.621	0.660	---	---	39.10	41.05*	---	---	---	---	---	---	---	1973 86213	
		0.06			54.7	2.000	0.062	0.622	0.730	---	---	39.70	41.76*	---	---	---	---	---	---	---	1973 86213	
		0.06			54.7	2.000	0.062	0.624	0.890	---	---	39.30	41.42*	---	---	---	---	---	---	---	1973 86213	
T6	S	0.06	R. T.	T-L	54.2	2.000	0.062	0.622	0.790	---	---	35.80	37.66*	---	---	---	---	---	---	---	1973 86213	
		0.06			54.2	2.000	0.062	0.623	0.840	---	---	36.00	37.87*	---	---	---	---	---	---	---	1973 86213	
		0.06			54.2	2.000	0.062	0.622	0.880	---	---	35.10	36.92*	---	---	---	---	---	---	---	1973 86213	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

CONDITION	ALUMINUM		TEST SPEC OR TEMP (F)	YIELD STR (KSI)	SPECIMEN				CRACK LENGTH				GROSS STRESS		K (APP) STAN		K (C) STAN			
	FORM	THICK (IN)			WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	W	B	2A(D)	2A(F)	S(O)	S(MAX)	K (KSI*SQRT IN)	MEAN DEV	K (KSI*SQRT IN)	MEAN DEV
BUCKLING OF CRACK EDGES RESTRAINED																				
T62 (GG)	S	0.13	R.T.	L-T	58.7	5.980	0.126	2.010	---	29.71	56.60	---	---	91.80	---	---	---	---	1978 GD005	
T62 (GG)	S	0.13	R.T.	L-T	58.7	15.970	0.126	4.000	---	28.87	75.30	---	---	82.30	---	---	---	---	1978 GD005	
T62 (GG)	S	0.13	R.T.	T-L	57.0	5.990	0.125	2.030	---	27.17	76.40	---	---	75.9/ 0.8	143.70*	---	---	---	1978 GD005	
					57.0	5.990	0.125	1.960	---	25.78	49.40	---	---	64.00	---	---	---	---	1978 GD005	
									---	27.78	52.20	---	---	62.00	63.0/ 1.4	---	---	---	1978 GD005	
BUCKLING OF CRACK EDGES RESTRAINED																				
T62 (WG)	S	0.13	R.T.	L-T	---	5.980	0.126	1.990	---	28.40	53.90	---	---	81.20	---	---	---	---	1978 GD005	
					---	6.000	0.125	2.080	---	27.87	54.50	---	---	73.00	77.1/ 5.8	---	---	---	1978 GD005	
T62 (WG)	S	0.13	R.T.	L-T	---	15.980	0.126	4.000	---	29.37	76.60	---	---	139.20	---	---	---	---	1978 GD005	
T62 (WG)	S	0.13	R.T.	T-L	---	5.980	0.126	1.960	---	27.45	51.60	---	---	70.90	---	---	---	---	1978 GD005	
					---	5.990	0.125	1.960	---	27.51	51.70	---	---	73.80	72.4/ 2.1	---	---	---	1978 GD005	
BUCKLING OF CRACK EDGES RESTRAINED																				
T81	S	0.04	R.T.	L-T	65.6	6.450	0.040	2.500	---	21.90	47.92	---	---	---	---	---	---	---	1966 86734	
					65.6	6.450	0.040	2.100	---	21.90	42.59	---	---	---	---	---	---	---	1966 86734	
					65.6	6.450	0.040	2.250	---	23.70	48.23	---	---	46.2/ 3.2	---	---	---	---	1966 86734	
T81	S	0.04	R.T.	L-T	65.1	9.700	0.040	4.000	---	19.69	55.27	---	---	---	---	---	---	---	1966 86734	
T81	S	0.13	R.T.	L-T	64.8	5.980	0.125	2.010	---	30.64	58.60	---	---	91.10*	---	---	---	---	1978 GD005	
					64.8	5.990	0.126	1.990	---	28.09	53.30	---	---	62.70	---	---	---	---	1978 GD005	
					64.8	5.990	0.126	2.010	---	28.35	54.20	---	---	55.4/ 2.8	68.10	65.4/ 3.8	---	---	1978 GD005	
T81	S	0.06	R.T.	T-L	62.0	6.000	0.060	2.000	2.500	---	27.10	51.62	---	---	60.29	---	---	---	1966 86734	

*NOTE- NET SECTION: STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)		CRACK LENGTH CROSS STRESS															
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	SPECIMEN		INIT		FINAL		ONSET		MAX		K (APP)		STAN		K (C)			
				WIDTH (IN)	THICK (IN)	2A(O)	2A(F)	2A(O)	2A(F)	2A(O)	2A(F)	2A(O)	2A(F)	2A(O)	2A(F)	2A(O)	2A(F)	2A(O)	2A(F)	2A(O)	2A(F)
BUCKLING OF CRACK EDGES RESTRAINED																					
T81	S	0.06	R. T.	T-L	62.0	15.000	0.060	5.000	6.000	---	18.90	56.92	64.51	1966	86734						
T81	S	0.06	R. T.	T-L	62.0	18.000	0.060	6.000	7.000	---	18.50	61.03	67.78	1966	86734						
T81	S	0.06	R. T.	T-L	62.0	21.000	0.060	7.000	8.200	---	17.60	62.71	69.85	1966	86734						
T81	S	0.06	R. T.	T-L	62.0	24.000	0.060	8.000	9.100	---	16.40	62.47	68.15	1966	86734						
T81	S	0.13	R. T.	T-L	64.1	5.990	0.126	2.020	---	---	23.32	44.70	59.50	1978	GD005						
T81	S	0.13	R. T.	T-L	64.1	6.000	0.126	1.980	---	---	22.88	43.30	55.70	1978	GD005						
T81	S	0.13	R. T.	T-L	64.1	6.010	0.126	2.060	---	---	23.24	45.10	56.80	1978	GD005						
BUCKLING OF CRACK EDGES NOT RESTRAINED																					
T81	S	0.06	R. T.	L-T	67.0	9.000	0.065	2.950	---	---	28.50	65.76	---	1966	86734						
T81	S	0.06	R. T.	L-T	68.0	2.000	0.062	0.625	1.040	---	36.00	37.94	55.61*	1973	86213						
T81	S	0.06	R. T.	L-T	68.0	2.000	0.061	0.619	1.065	---	36.10	37.82	56.99*	1973	86213						
T81	S	0.06	R. T.	L-T	68.0	2.000	0.061	0.619	0.940	---	38.20	40.02*	53.97*	1973	86213						
T81	S	0.06	R. T.	L-T	68.0	2.000	0.061	0.617	1.040	---	36.60	38.26	56.54*	1973	86213						
T81	S	0.06	R. T.	L-T	68.0	2.000	0.061	0.625	0.970	---	39.40	37.31	51.37*	1973	86213						
T81	S	0.06	R. T.	L-T	68.0	2.000	0.061	0.620	1.070	---	37.00	38.84	58.73*	1973	86213						
T81	S	0.06	R. T.	L-T	67.1	2.000	0.062	0.624	0.840	---	35.90	37.84	46.39*	1973	86213						
T81	S	0.06	R. T.	L-T	69.1	2.000	0.062	0.623	0.870	---	35.40	37.24	46.99*	1973	86213						
T81	S	0.06	R. T.	L-T	69.1	2.000	0.062	0.623	0.960	---	36.50	38.39	52.90*	1973	86213						
T81	S	0.06	R. T.	L-T	59.0	9.000	0.064	3.320	---	---	27.70	69.15	---	1966	86734						
T81	S	0.06	R. T.	L-T	59.0	9.000	0.065	3.380	---	---	28.70	72.54	70.8/ 2.4	1966	86734						
T81	S	0.06	R. T.	L-T	59.0	20.000	0.065	11.500	---	---	14.00	75.62	---	1966	86734						
T81	S	0.06	R. T.	L-T	59.0	20.000	0.065	11.290	---	---	14.70	77.58	76.6/ 1.4	1966	86734						

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD DEV

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)		CRACK LENGTH CROSS STRESS																
CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST SPEC TEMP (F)	OR STR (KSI)	---SPECIMEN---		INIT		FINAL		ONSET		MAX		K (APP)		STAN		K (C)		STAN DEV DATE REFER	
					WIDTH (IN)	THICK B	(IN)	2A(O)	(IN)	2A(F)	(KSI)	S(O)	(KSI)	S(MAX)	(KSI*SQRT IN)	MEAN DEV	(KSI*SQRT IN)	MEAN DEV				
T81	S	0.12	R. T.	L-T	64.9	3.000	0.125	1.040	1.660	---	33.90	46.89	---	68.14*	---	---	---	---	---	---	---	1973 86213
		0.12			64.9	3.000	0.125	1.000	1.580	---	33.70	45.39	---	64.53*	---	---	---	---	---	---	---	1973 86213
		0.12			64.9	3.000	0.125	1.060	1.620	---	33.10	46.33	---	64.93*	---	---	---	---	---	---	---	1973 86213
		0.12			65.2	3.000	0.123	1.070	1.680	---	32.70	46.06	---	66.53*	---	---	---	---	---	---	---	1973 86213
		0.12			65.2	3.000	0.123	1.000	1.550	---	35.20	47.41*	---	66.20*	---	---	---	---	---	---	---	1973 86213
		0.12			65.2	3.000	0.123	1.080	1.670	---	34.00	48.19*	---	69.61*	---	---	---	---	---	---	---	1973 86213
T81	S	0.06	250	L-T	59.0	9.000	0.065	3.600	---	32.40	89.66*	---	---	---	---	---	---	---	---	---	---	1966 86734
T81	S	0.06	R. T.	T-L	66.7	2.000	0.061	0.617	0.985	---	33.30	34.81	---	48.93*	---	---	---	---	---	---	---	1973 86213
		0.06			66.7	2.000	0.061	0.625	0.980	---	35.20	37.10	---	51.54*	---	---	---	---	---	---	---	1973 86213
		0.06			66.7	2.000	0.061	0.613	0.760	---	33.70	35.09	---	48.47*	---	---	---	---	---	---	---	1973 86213
		0.06			66.7	2.000	0.061	0.625	1.065	---	35.40	37.31	---	55.88*	---	---	---	---	---	---	---	1973 86213
		0.06			66.7	2.000	0.061	0.625	0.940	---	33.00	34.78	---	46.63*	---	---	---	---	---	---	---	1973 86213
		0.06			66.7	2.000	0.061	0.617	0.985	---	33.60	35.13	---	49.37*	---	---	---	---	---	---	---	1973 86213
		0.06			67.2	2.000	0.062	0.622	0.840	---	32.30	33.98	---	41.74*	---	---	---	---	---	---	---	1973 86213
		0.06			67.2	2.000	0.062	0.623	0.860	---	34.40	36.18	---	45.26*	---	---	---	---	---	---	---	1973 86213
		0.06			67.2	2.000	0.062	0.622	0.950	---	33.60	35.34	---	47.90*	---	---	---	---	---	---	---	1973 86213
T81	S	0.06	R. T.	T-L	62.0	6.000	0.060	2.000	2.420	---	25.60	48.76	---	55.60	---	---	---	---	---	---	---	1966 86734
		0.06			62.0	6.000	0.060	2.000	2.360	---	28.20	53.71	---	60.14	---	---	---	---	---	---	---	1966 86734
T81	S	0.06	R. T.	T-L	62.0	9.000	0.060	3.000	3.700	---	24.80	57.85	---	66.90	---	---	---	---	---	---	---	1966 86734
		0.06			62.0	9.000	0.060	3.000	3.260	---	23.20	54.12	---	57.20	---	---	---	---	---	---	---	1966 86734
		0.06			62.0	9.000	0.060	3.000	3.500	---	23.00	53.65	---	59.59	---	---	---	---	---	---	---	1966 86734
T81	S	0.06	R. T.	T-L	62.0	15.000	0.060	5.000	5.600	---	16.80	50.59	---	54.60	---	---	---	---	---	---	---	1966 86734
		0.06			62.0	15.000	0.060	5.000	5.600	---	16.80	50.59	---	54.60	---	---	---	---	---	---	---	1966 86734
T81	S	0.06	R. T.	T-L	62.0	18.000	0.060	6.000	6.640	---	15.60	51.46	---	55.08	---	---	---	---	---	---	---	1966 86734
		0.06			62.0	18.000	0.060	6.000	6.600	---	15.40	50.80	---	54.14	---	---	---	---	---	---	---	1966 86734
T81	S	0.06	R. T.	T-L	62.0	21.000	0.060	7.000	8.200	---	14.60	52.02	---	57.95	---	---	---	---	---	---	---	1966 86734
		0.06			62.0	21.000	0.060	7.000	8.000	---	13.80	49.17	---	53.82	---	---	---	---	---	---	---	1966 86734

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)																																								
CONDITION	--PRODUCT-- FORM THICK TEMP OR (IN) (F)	TEST SPEC YIELD STR (KSI)	CRACK LENGTH GROSS STRESS				K(C) STAN MEAN DEV DATE REFER																																					
			WIDTH (IN)	THICK (IN)	INIT 2A(D)	FINAL 2A(F)		ONSET S(O)	MAX S(MAX)																																			
BUCKLING OF CRACK EDGES NOT RESTRAINED																																												
T81	S	0 06 R.T. T-L	0 060	0 060	8 000	8 800	13 00	49 52	47 62	48.6/ 1.3	52.2/ 0.9	1966 86734																																
													0 060	8 000	9 000	12 50	47 62	51.54	1966 86734																									
T81	S	0 12 R.T. T-L	0 125	0 125	1 000	1 470	31 20	42 02	42 26	42 26	55.95*	1973 86213																																
													0 12	3 000	1 070	1 600	30 00	42 26	58.14*	1973 86213																								
																					0 12	3 000	1 070	1 480	30 00	42 26	54.12*	1973 86213																
																													0 12	3 000	1 060	1 420	30 50	42 69	53.09*	1973 86213								
																																					0 12	3 000	1 000	1 340	31 00	41.75	51.46*	1973 86213

ALUMINUM		2024		K(C)																																																																																																		
CONDITION	--PRODUCT-- FORM THICK TEMP OR (IN) (F)	TEST SPEC YIELD STR (KSI)	CRACK LENGTH GROSS STRESS				K(C) STAN MEAN DEV DATE REFER																																																																																															
			WIDTH (IN)	THICK (IN)	INIT 2A(D)	FINAL 2A(F)		ONSET S(O)	MAX S(MAX)																																																																																													
BUCKLING OF CRACK EDGES NOT RESTRAINED																																																																																																						
T851	S	0 12 R.T. L-T	0 125	0 125	1 000	1 510	19 50	31 50	42 42	42 90	57.84*	1973 86213																																																																																										
													0 12	3 000	1 090	1 530	14 50	29 00	41 37	53.89*	1973 86213																																																																																	
																						0 12	3 000	1 110	1 510	16 90	29 70	42 90	54.54*	1973 86213																																																																								
																															0 12	3 000	1 000	1 530	18 70	32 30	43 50	53.30*	1973 86213																																																															
																																								0 12	3 000	1 080	1 700	15 50	29 40	41 67	60.56*	1973 86213																																																						
																																																	0 12	3 000	1 100	1 520	15 30	28 60	41 05	52.83*	1973 86213																																													
																																																										0 12	3 000	1 000	1 400	19 90	31 60	42 56	54.36*	1973 86213																																				
																																																																			0 12	3 000	1 000	1 500	19 50	32 40	43 64	59.14*	1973 86213																											
																																																																												0 12	3 000	1 000	1 300	17 40	30 70	41 35	49.76*	1973 86213																		
																																																																																					0 12	3 000	1 070	1 430	14 60	28 60	40 29	50.08*	1973 86213									
																																																																																														0 12	3 000	1 050	1 460	20 40	30 90	41 62	55.08*	1973 86213
0 12	3 000	0 132	1 000	1 640	---	34 20	46 06*	67.91*	1973 86213																																																																																													
										0 12	3 000	0 132	1 090	1 740	---	33 20	47 36*	70.11*	1973 86213																																																																																			
0 12	3 000	0 132	1 060	1 750	---	33 20	46 47*	42.0/ 1.0	70 55*	---	1973 86213																																																																																											

T851	P	0 25 R.T. L-T	0 242	1 330	2 140	31 90	49 53	71 60*	1973 86213								
										0 242	1 330	2 140	30 90	47 97	69 36*	1973 86213	
0 25	4 000	0 243	1 410	2 390	30 00	48 41	72 13*	1973 86213									
									0 25	4 000	0 256	1 330	2 210	33 80	52 48	78 33*	1973 86213

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 7.5.2.2 (Con't)

CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	WIDTH (IN)	THICK (IN)	B	CRACK LENGTH				GROSS STRESS	K (APP)		K (C)		STAN	REFER											
								INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)		MEAN (KSI)	DEV (KSI)	MEAN (KSI)	DEV (KSI)													
T851	P	1.00	R. T.	L-T	65.8	20.000	1.000	7.000	9.170	---	10.70	38.42	46.84	1973	86213	---	---	---	---										
																				1.000	7.000	9.920	---	11.20	40.22	52.41	1973	86213	
																				1.000	7.000	9.970	---	11.00	39.50	49.70	1973	86213	
																				1.000	7.000	9.940	---	10.70	38.42	48.41	1973	86213	
																				1.000	7.000	9.680	---	11.40	40.94	52.22	1973	86213	
																				1.000	7.000	9.300	---	10.90	39.14	48.27	1973	86213	
																				1.000	7.000	9.300	---	11.50	41.30	50.73	1973	86213	
																				1.000	7.000	10.090	---	11.50	41.30	54.44	1973	86213	
																				1.000	7.000	9.250	---	10.00	35.91	44.09	1973	86213	
																				1.000	7.000	9.170	---	10.70	38.42	46.84	1973	86213	
																				1.000	7.000	9.710	---	9.80	35.19	45.01	1973	86213	
																				1.000	7.000	8.900	---	9.70	34.83	41.45	1973	86213	
																				1.000	7.000	8.900	---	9.70	34.83	38.67	1973	86213	
																				1.000	7.000	8.900	---	9.70	34.83	48.47	1973	86213	
																				T851	S	0.12	R. T.	T-L	64.4	3.000	0.125	1.000	1.300
0.125	1.100	1.490	12.90	26.00	37.32	47.18*	1973	86213																					
0.120	1.130	1.450	13.80	25.00	36.56	44.30	1973	86213																					
0.124	1.000	1.420	19.40	25.90	34.88	45.09	1973	86213																					
0.125	1.000	1.320	19.40	25.10	39.19	47.74	1973	86213																					
0.125	1.100	1.560	13.90	25.40	36.46	48.06*	1973	86213																					
0.125	1.000	1.410	17.20	28.20	37.98	48.80*	1973	86213																					
0.125	1.070	1.380	14.80	26.90	37.87	45.73	1973	86213																					
0.125	1.120	1.490	15.00	24.30	35.32	44.09	1973	86213																					
0.125	1.050	1.300	15.80	26.90	37.41	43.60	1973	86213																					
0.125	1.000	1.300	18.00	28.20	37.98	45.71	1973	86213																					
0.125	1.000	1.250	16.70	26.40	35.95	41.93	1973	86213																					
0.132	1.060	1.600	---	29.70	41.97	57.56*	1973	86213																					
0.132	1.000	1.540	---	32.10	43.23	60.01*	1973	86213																					
0.132	1.060	1.580	---	30.00	41.99	57.44*	1973	86213																					
T851	P	0.25	R. T.	T-L	56.6	3.000	0.245	1.120	1.320	---	17.00	24.71	27.89	1973	86213	---	---	---	---	---									
																					0.249	1.180	1.560	---	17.30	26.09	32.73	1973	86213
																					0.250	1.170	1.420	---	30.11	25.93	30.11	1973	86213
																					0.251	1.160	1.500	---	18.60	27.71	33.75	1973	86213
																					0.252	1.220	1.260	---	18.50	28.58	29.28	1973	86213
0.252	1.180	1.540	---	18.00	27.14	26.77	1973	86213																					

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

ALUMINUM		2024		K(C)		CRACK LENGTH GROSS STRESS																																												
CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST SPEC TEMP (F)	OR STR (KSI)	WIDTH (IN)	---SPECIMEN---		INIT		FINAL		ONSET		MAX		K(APP)		STAN		K(C)		STAN																												
						H	B	2A(O)	2A(F)	S(O)	S(MAX)	K(SI)	K(SI)	K(SI)	K(SI)	MEAN	DEV	MEAN	DEV	MEAN	DEV	DATE	REFER																											
T851	P	0.25	R. T.	T-L	66.2	4.000	0.243	1.330	1.900	---	25.00	38.81	50.40	47.82	48.40	95.45	55.41	35.11	37.36	47.1/ 8.1	1973	86213	1973	86213																										
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---							
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---			
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---		
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
T851	P	1.00	R. T.	T-L	64.4	20.000	1.000	7.000	9.200	---	7.10	25.50	31.14	32.57	31.32	72.5	33.27	33.73	35.49	37.27	32.53	36.25	47.1/ 8.1	1973	86213																									
																										---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---				
																										---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
																										---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
																										---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
																										---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---
T86	S	0.06	R. T.	L-T	72.4	2.000	0.064	0.619	0.820	---	35.90	37.61	45.56*	47.72*	45.11*	56.16*	51.63*	49.07*	49.63*	44.44*	50.31*	38.4/ 1.4	1973	86213																										
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---				
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---		
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	
																									---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	---	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.5.2.2 (Con't)

CONDITION	ALUMINUM		2024		K(C)		CRACK LENGTH		GROSS STRESS		K(C) STAN		K(C) STAN					
	FORM	THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI)	MEAN (IN)	DEV (KSI)	MEAN (IN)	DEV (IN)			
TB6	S	0.06	R. T.	72.9	15.800	0.064	3.000	3.400	---	22.20	49.29	52.82	---	52.82	---	1973 86213		
			L-T	72.9	15.810	0.063	6.010	6.930	---	16.10	54.40	60.45	---	60.45	---	1973 86213		
				72.9	15.810	0.064	3.990	4.660	---	18.20	47.44	52.06	---	52.06	---	1973 86213		
				72.9	15.820	0.064	5.990	6.800	---	12.80	43.14	47.35	---	47.35	---	1973 86213		
TB6	S	0.06	R. T.	70.8	2.000	0.064	2A(D)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
							2A(F)	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213	
							2A(I)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
							2A(O)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
							2A(F)	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213	
							2A(I)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
							2A(O)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
							2A(F)	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213	
							2A(I)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
							2A(O)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
							2A(F)	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213	
							2A(I)	1.010	1.420	---	34.70	43.82	47.6/	4.6	52.08	53.0/	4.7	1973 86213
TB6	S	0.06	R. T.	70.8	2.000	0.064	2A(D)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
							2A(F)	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213		
							2A(I)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
							2A(O)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
							2A(F)	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213		
							2A(I)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
							2A(O)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
							2A(F)	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213		
							2A(I)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
							2A(O)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
							2A(F)	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213		
							2A(I)	0.624	0.870	---	32.20	33.94	42.75*	---	42.75*	---	1973 86213	
TB6	S	0.06	R. T.	71.2	15.810	0.063	3.010	3.430	---	19.70	43.82	47.10	---	47.10	---	1973 86213		
							3.430	---	19.70	43.82	47.10	---	47.10	---	1973 86213			
							3.010	3.430	---	19.70	43.82	47.10	---	47.10	---	1973 86213		
							3.430	---	19.70	43.82	47.10	---	47.10	---	1973 86213			
TB6	S	0.06	R. T.	71.2	15.820	0.063	3.020	3.360	---	21.90	47.91	50.81	---	50.81	---	1973 86213		
							3.360	---	21.90	47.91	50.81	---	50.81	---	1973 86213			
							3.020	3.360	---	21.90	47.91	50.81	---	50.81	---	1973 86213		
							3.360	---	21.90	47.91	50.81	---	50.81	---	1973 86213			
TB6	S	0.06	R. T.	71.2	15.820	0.064	4.000	4.620	---	15.70	40.98	44.67	---	44.67	---	1973 86213		
							4.620	---	15.70	40.98	44.67	---	44.67	---	1973 86213			
							4.000	4.620	---	15.70	40.98	44.67	---	44.67	---	1973 86213		
							4.620	---	15.70	40.98	44.67	---	44.67	---	1973 86213			
TB6	S	0.06	R. T.	71.2	15.820	0.064	1.000	1.200	---	31.90	40.08	42.9/	3.4	43.95	45.9/	3.2	1973 86213	
							1.200	---	31.90	40.08	42.9/	3.4	43.95	45.9/	3.2	1973 86213		
							1.000	1.200	---	31.90	40.08	42.9/	3.4	43.95	45.9/	3.2	1973 86213	
							1.200	---	31.90	40.08	42.9/	3.4	43.95	45.9/	3.2	1973 86213		

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

ALUM.
ALLOY

2024

SPECIMEN THK: .188"
SPECIMEN WIDTH: 4.000"
 K_C (ksi \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .19" TH SHEET
SPECIMEN TYPE: CCP
ORIENTATION: L-T

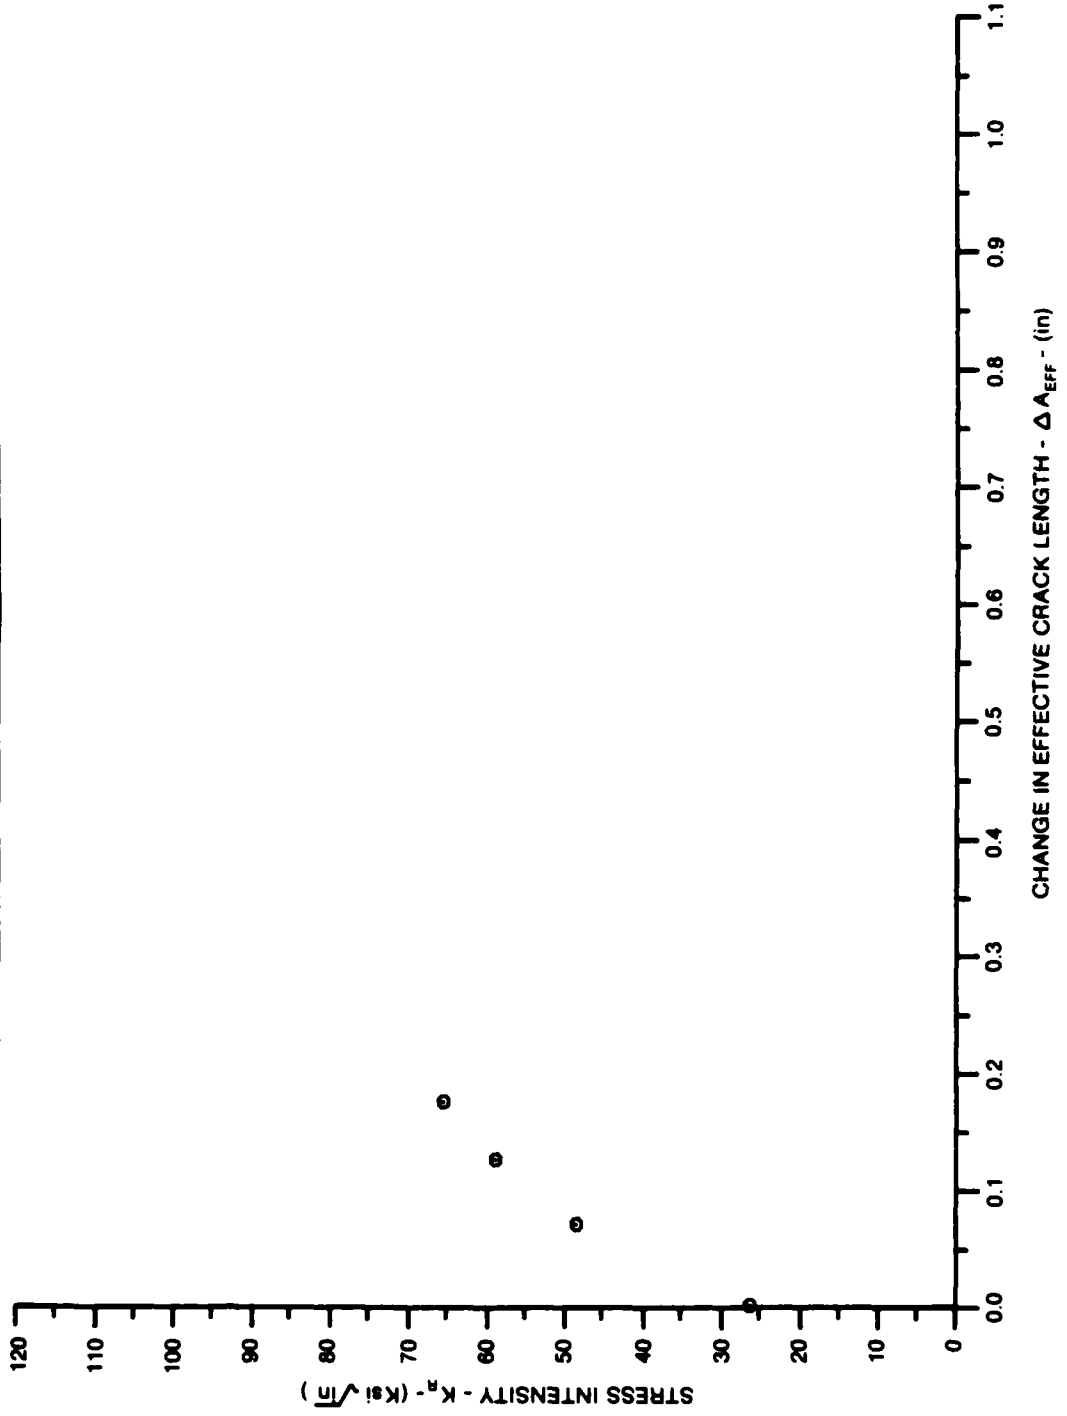


Figure 7.5.2.3

ALUM. ALLOY
2024

SPECIMEN THK: .191"
 SPECIMEN WIDTH: 4.000"
 K_{IC} (Ksi \sqrt{in}):
 REFERENCE: DAB01

CONDITION/HT: T351
 FORM: .19" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

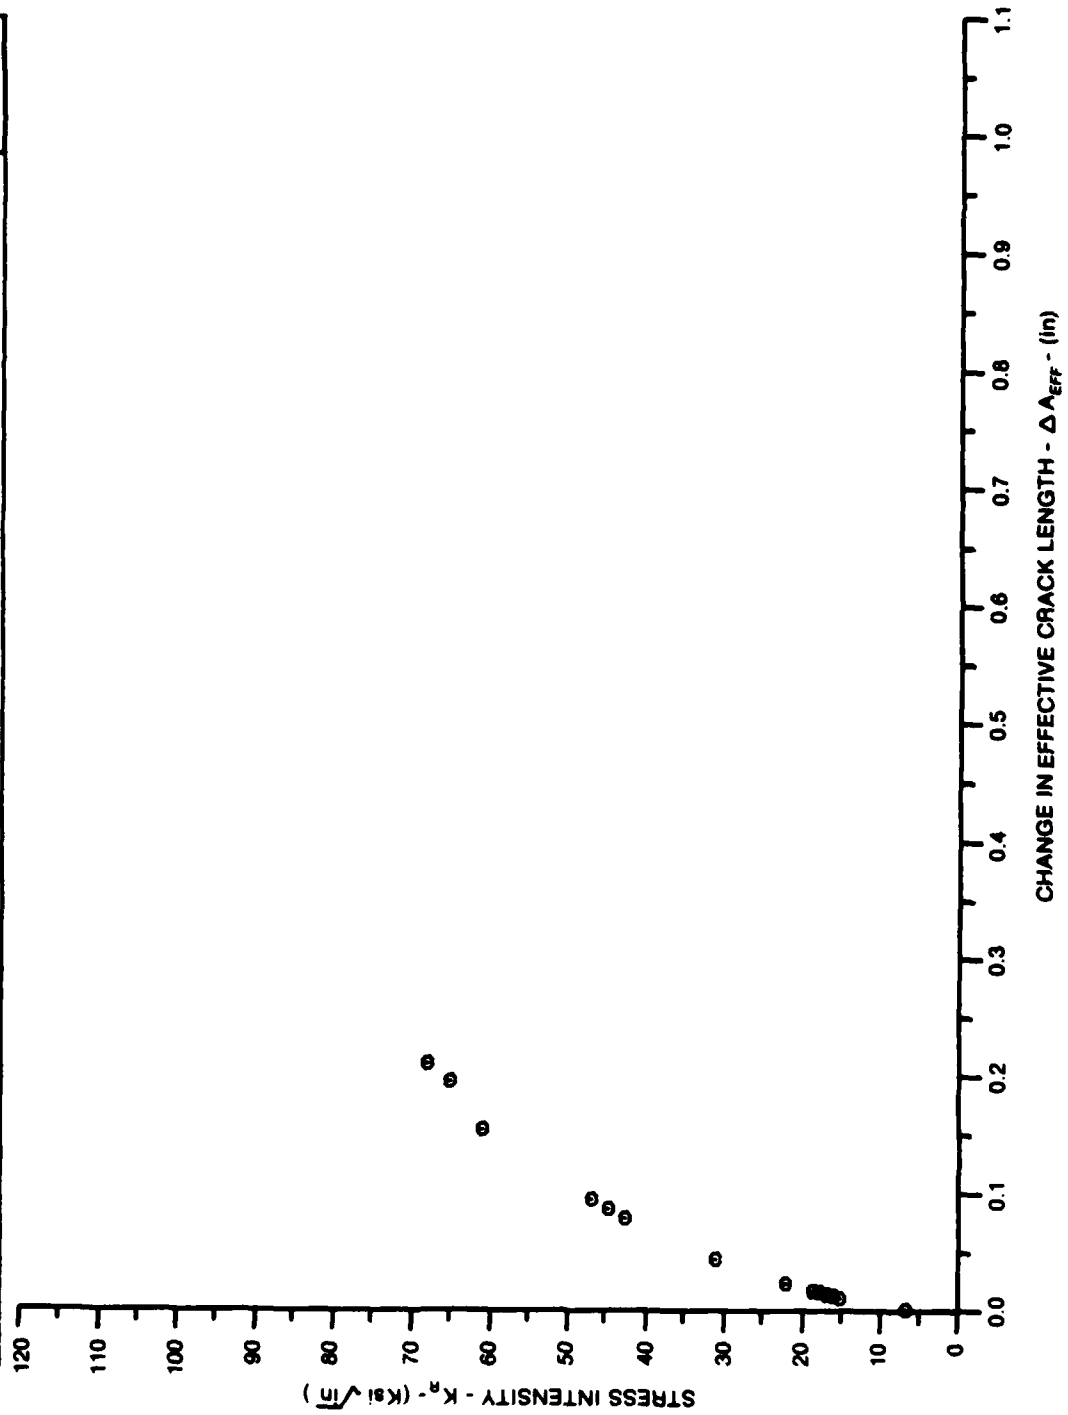


Figure 7.5.2.4

ALUM.
ALLOY

2024

SPECIMEN THK: 302"
SPECIMEN WIDTH: 4.000"
 K_{IC} (Ksi \sqrt{in}):
REFERENCE: DA001

CONDITION/HI: T351
FORM: .19" TH SHEET
SPECIMEN TYPE: CCP
ORIENTATION: L-T

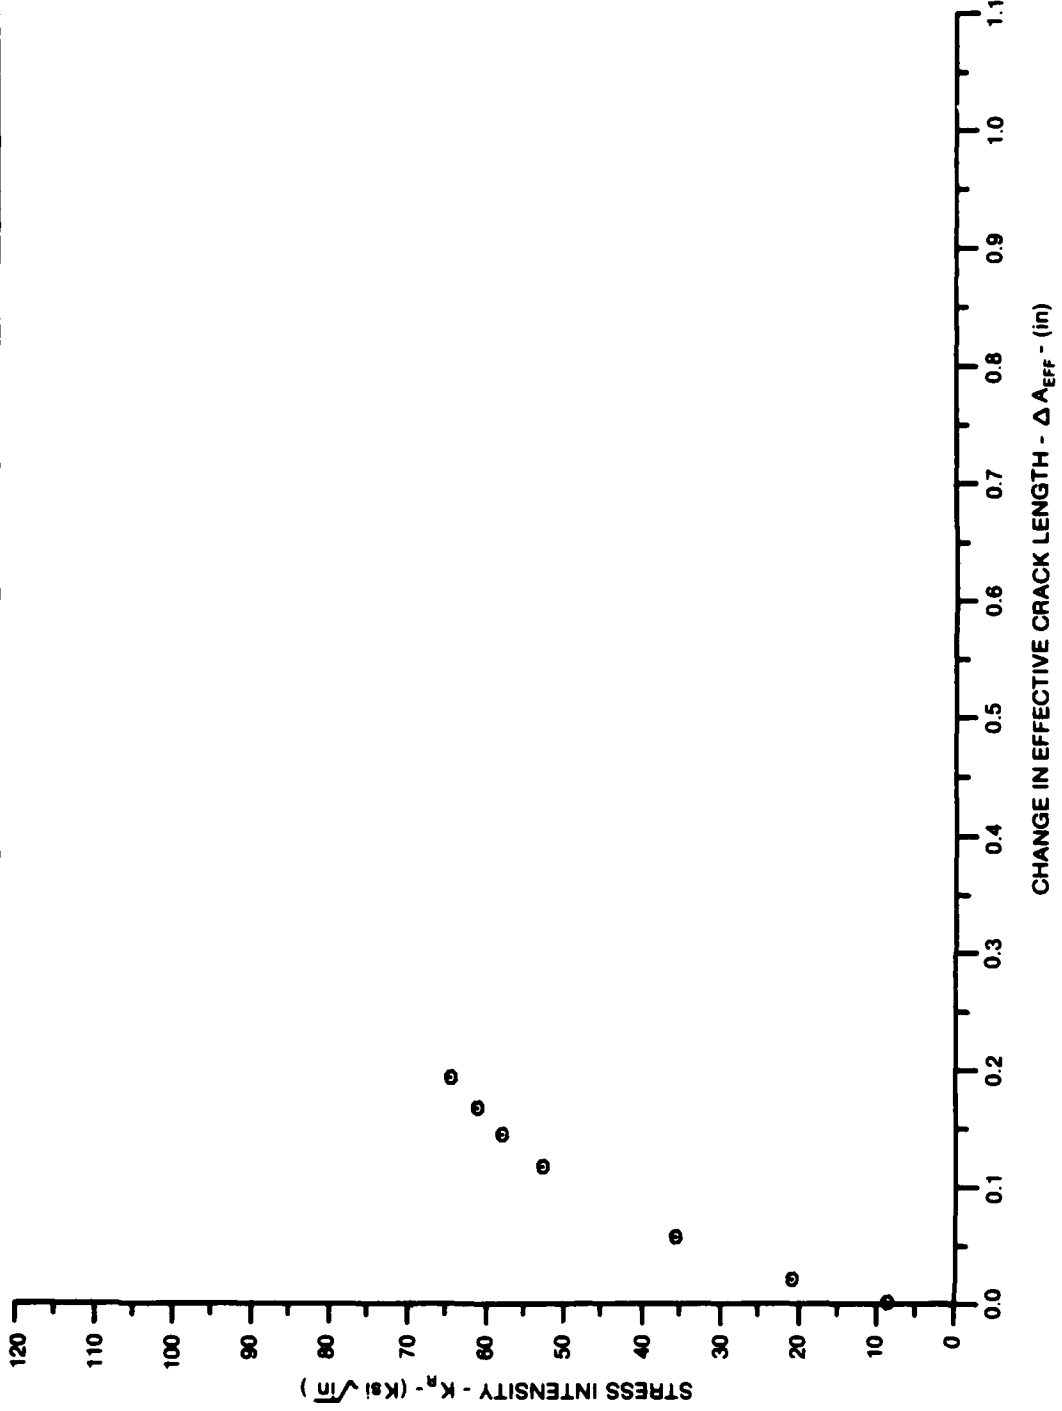


Figure 7.5.2.5

ALUM.
ALLOY

2024

SPECIMEN THK: .181"
SPECIMEN WIDTH: 11.888"
 K_{IC} (KSI \sqrt{in}):
REFERENCE: DA001

CONDITION: T351
FORM: .19" TH SHEET
SPECIMEN TYPE: CCP
ORIENTATION: L-T

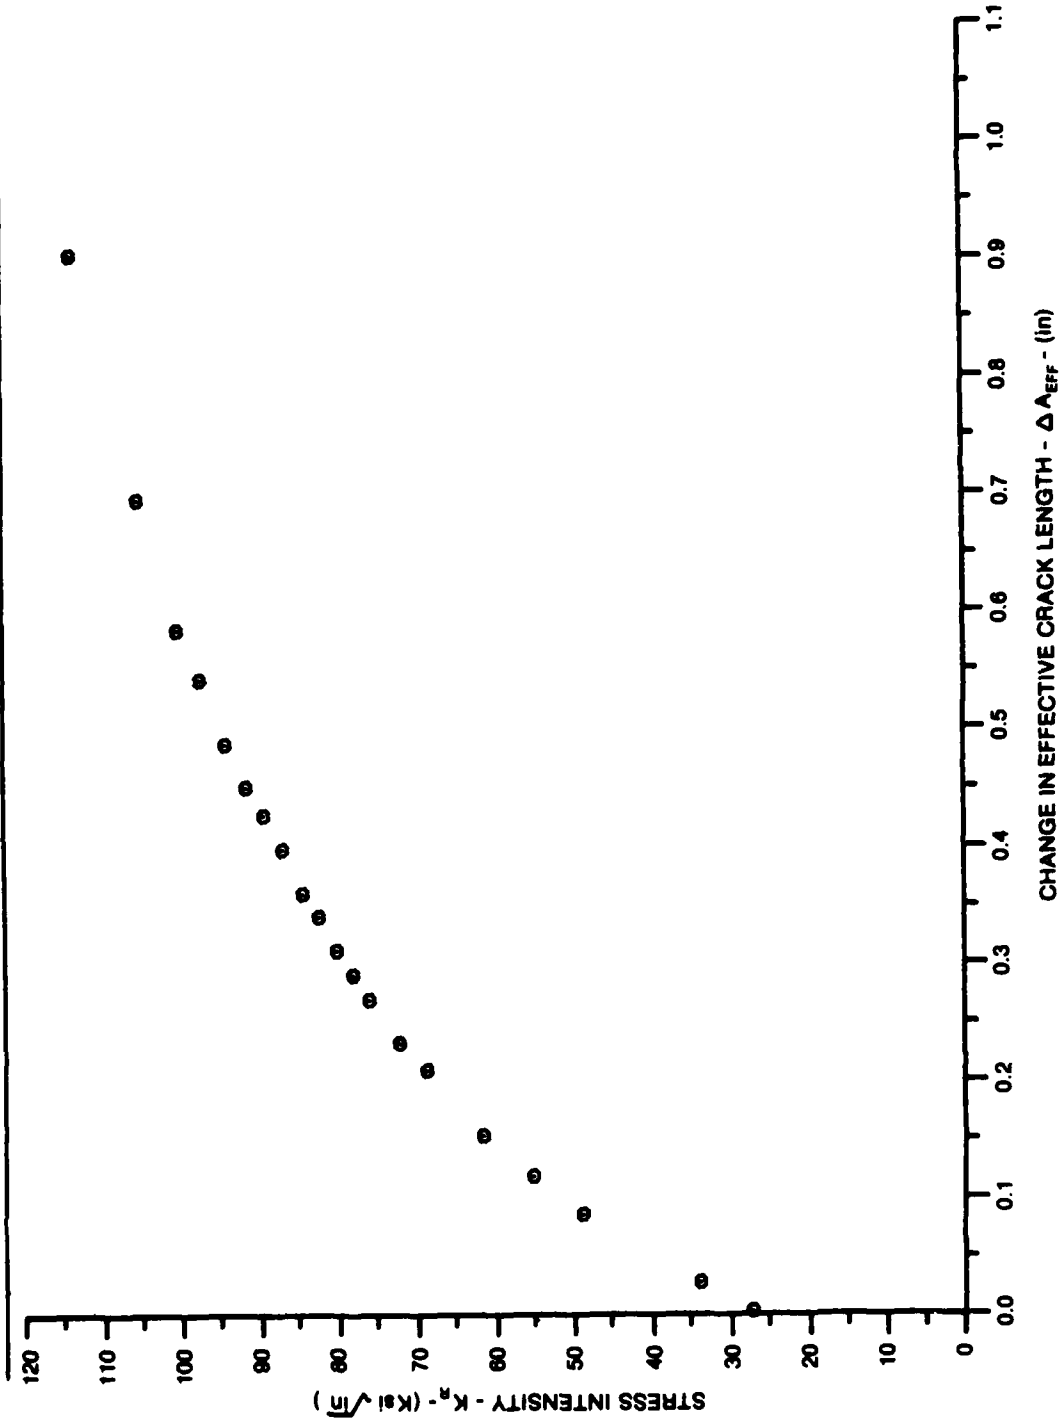


Figure 7.5.2.6

ALUM. ALLOY
2024

SPECIMEN THK: .104"
 SPECIMEN WIDTH: 12.002"
 K_C (Ksi \sqrt{in}):
 REFERENCE: DAB01

CONDITION: T351
 FORM: .10" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

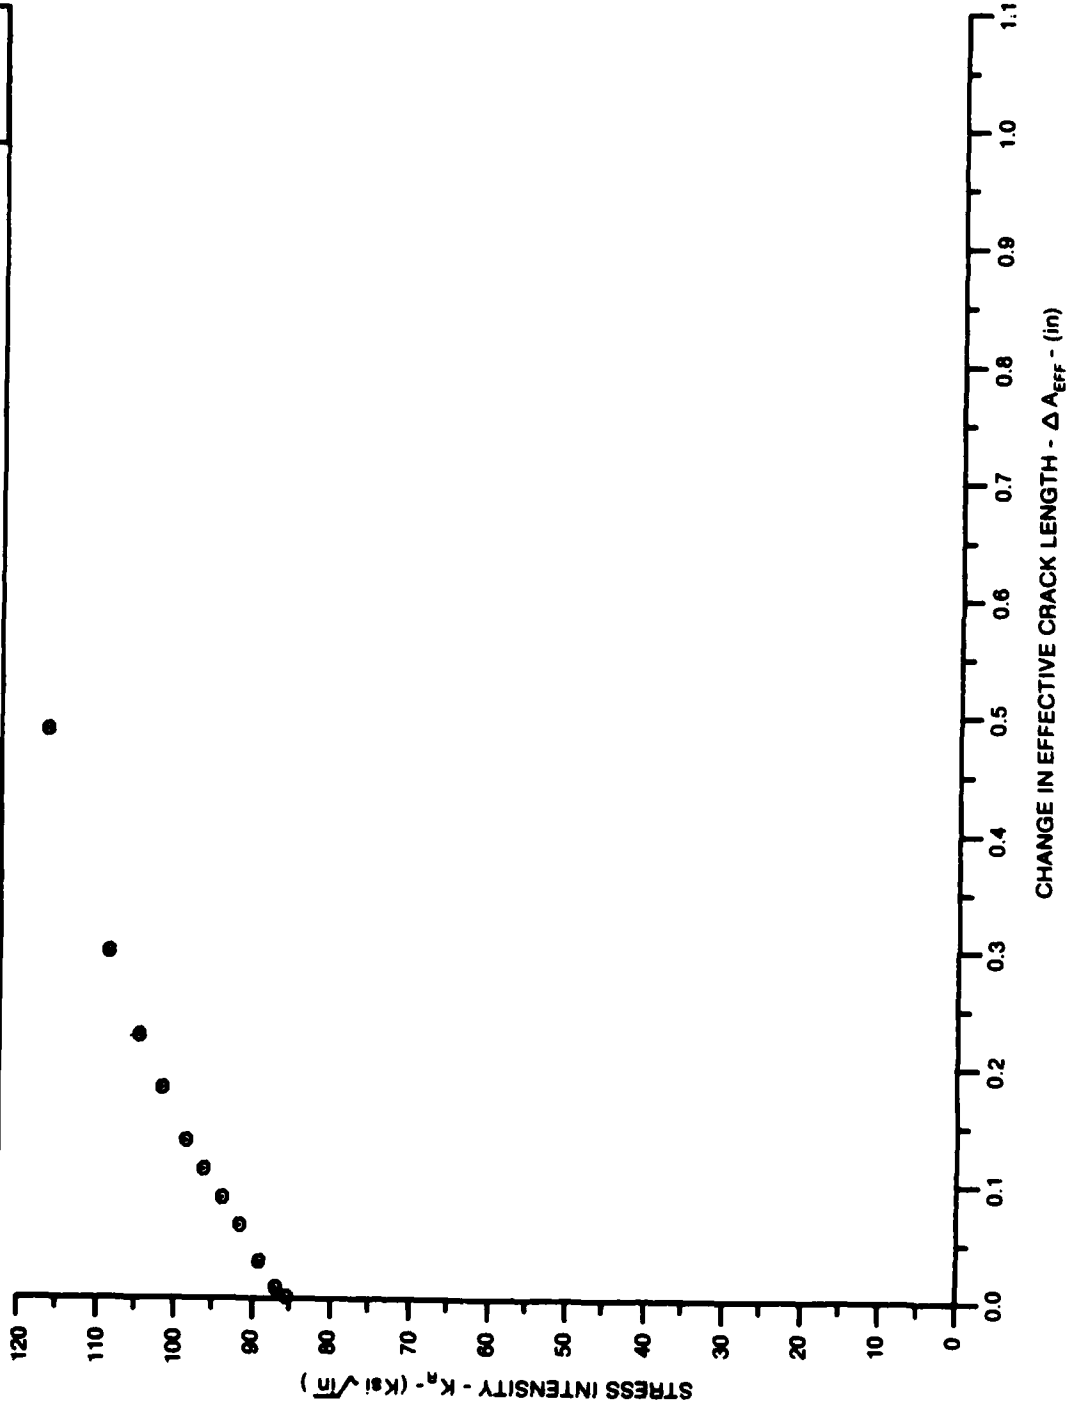


Figure 7.5.2.7

ALUM.
ALLOY

2024

SPECIMEN THK: .188"
SPECIMEN WIDTH: 11.997"
 K_C (KSI \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .18" TH SHEET
SPECIMEN TYPE: CCP
ORIENTATION: L-T

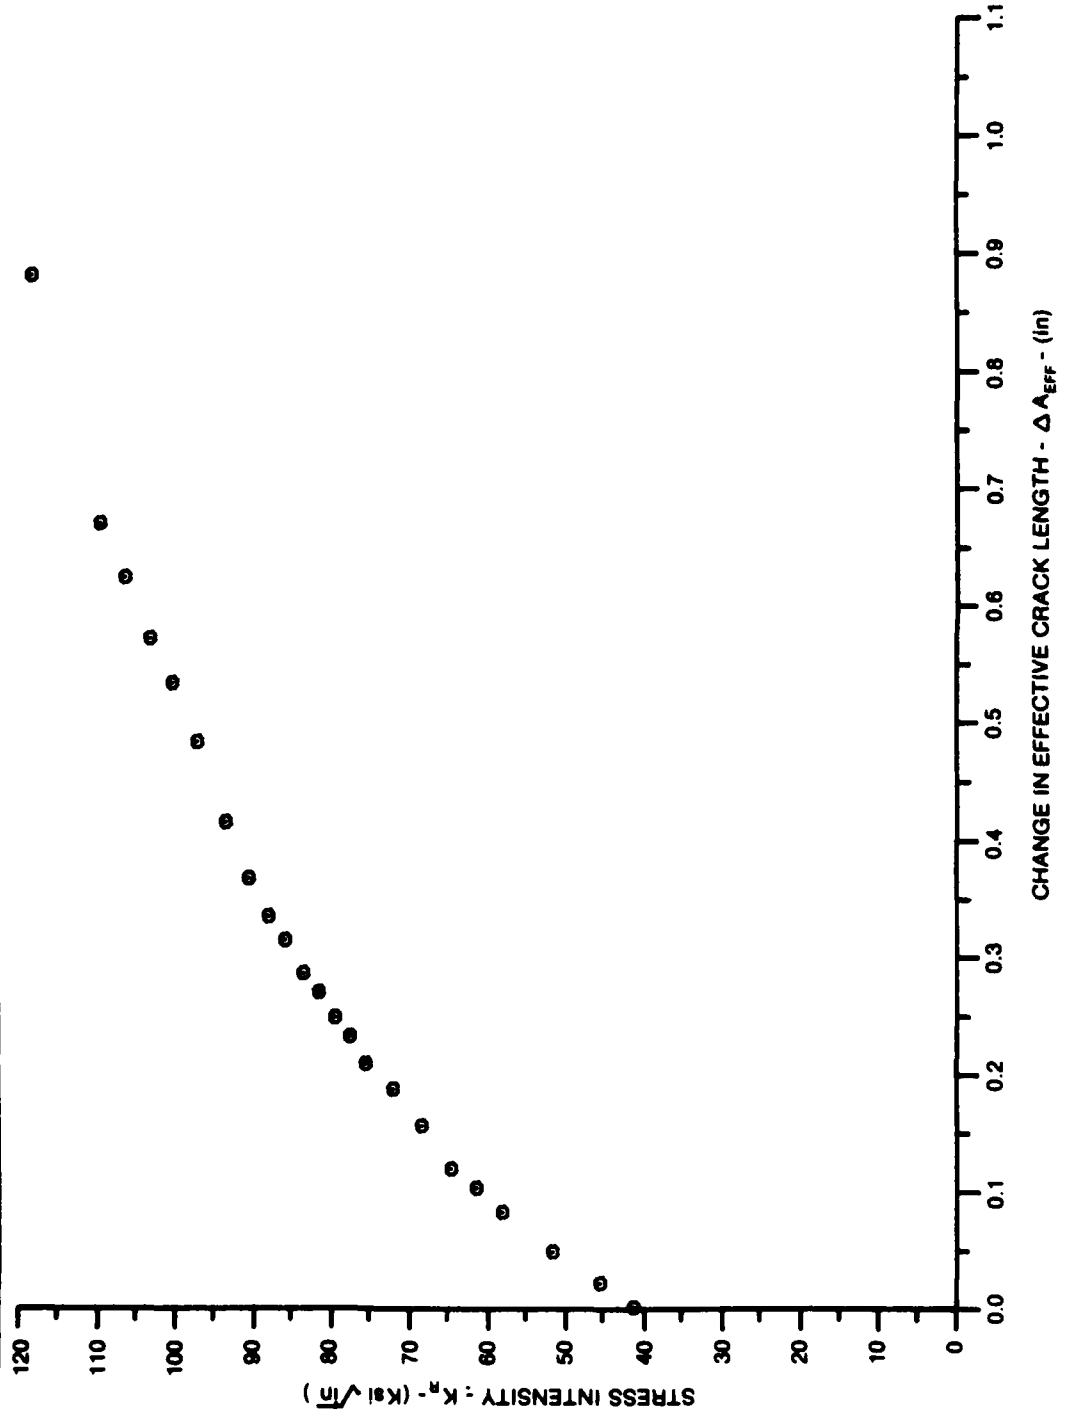


Figure 7.5.2.8

ALUM.
ALLOY

2024

SPECIMEN THK: .250"
SPECIMEN WIDTH: 4.000"
 K_{IC} (Ksi- \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

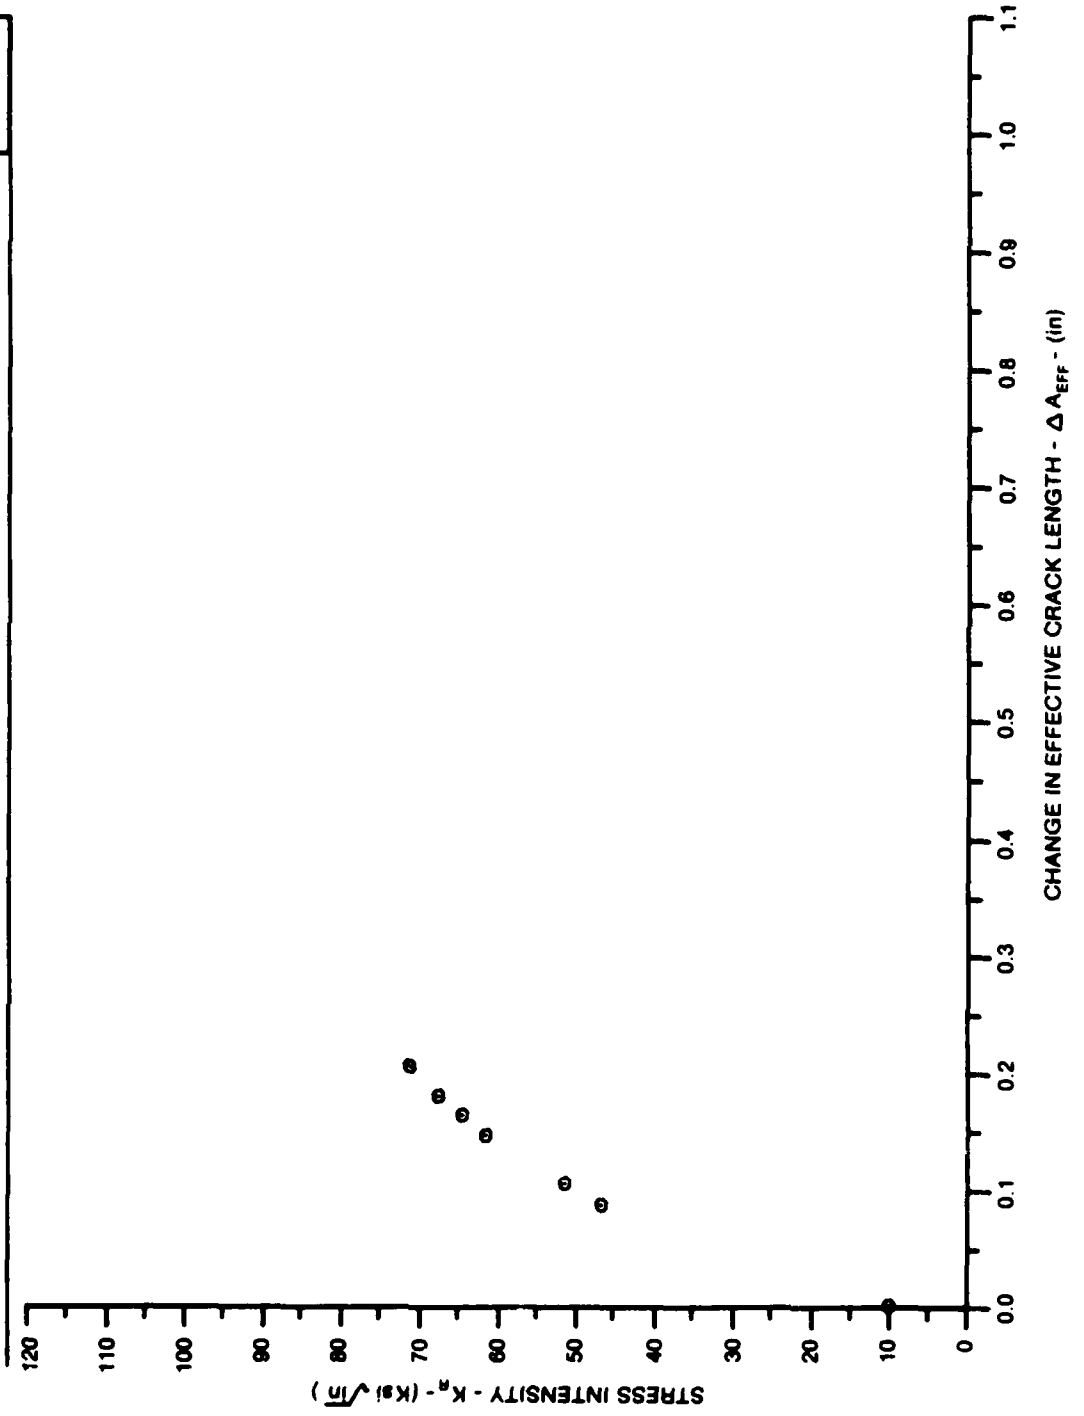


Figure 7.5.2.9

ALUM.
ALLOY

2024

SPECIMEN THK: .250"
SPECIMEN WIDTH: 4.002"
 K_{IC} (Ksi \sqrt{in}):
REFERENCE: DAB01

CONDITION/HT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

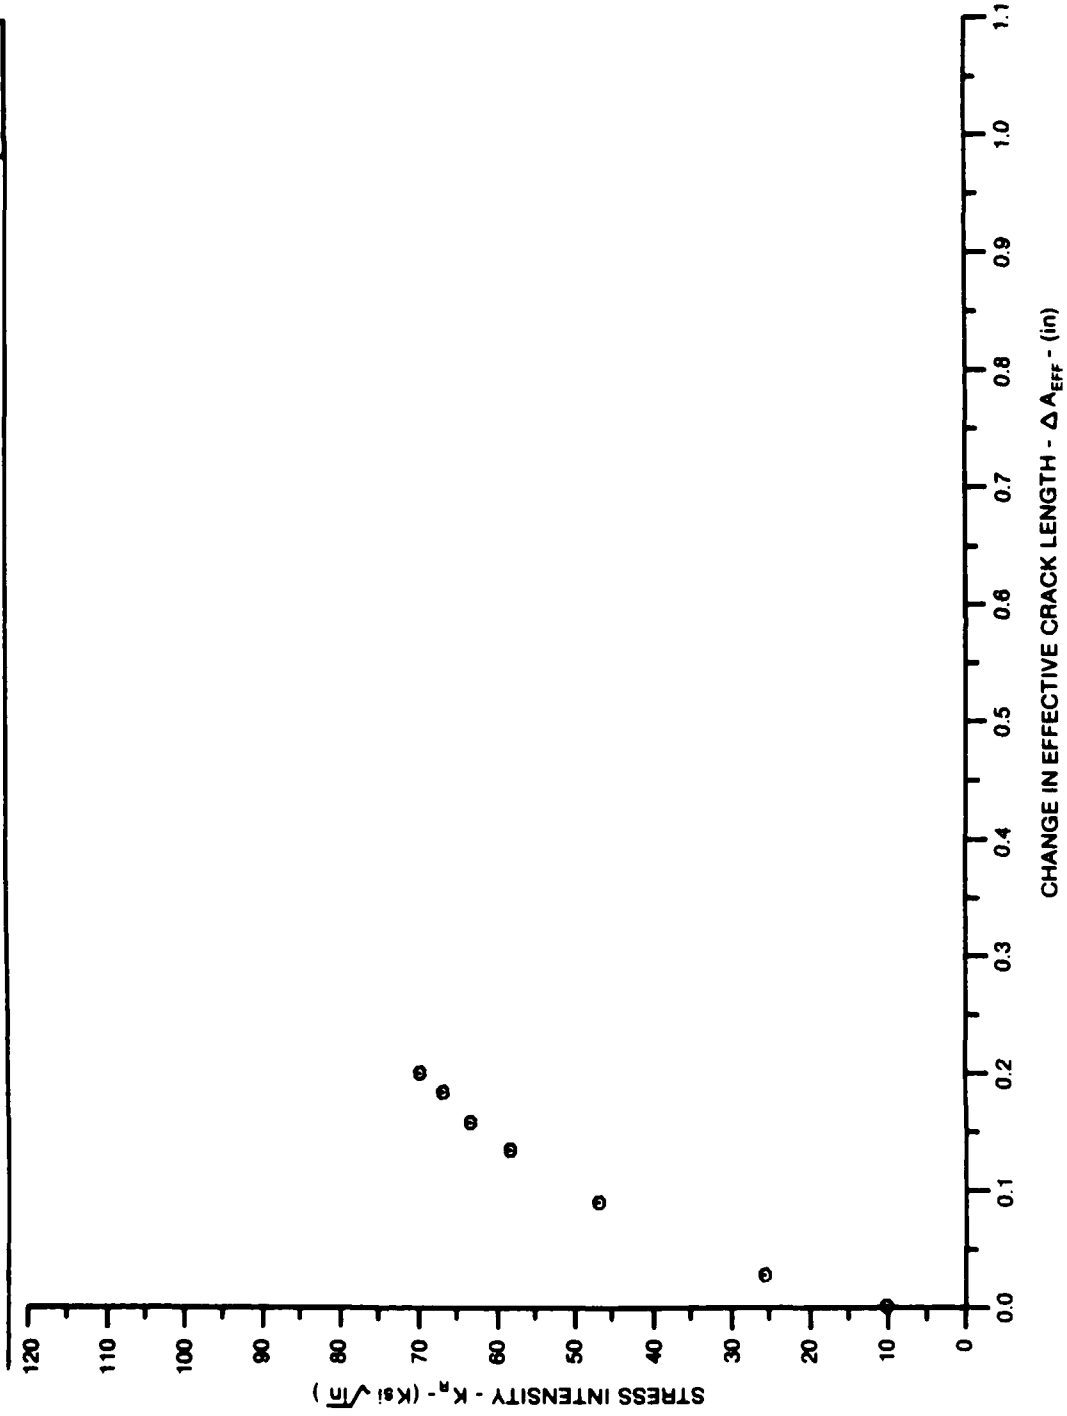


Figure 7.5.2.10

ALUM.
ALLOY

2024

SPECIMEN THK: .260"
SPECIMEN WIDTH: 4.000"
 K_C (Ksi \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

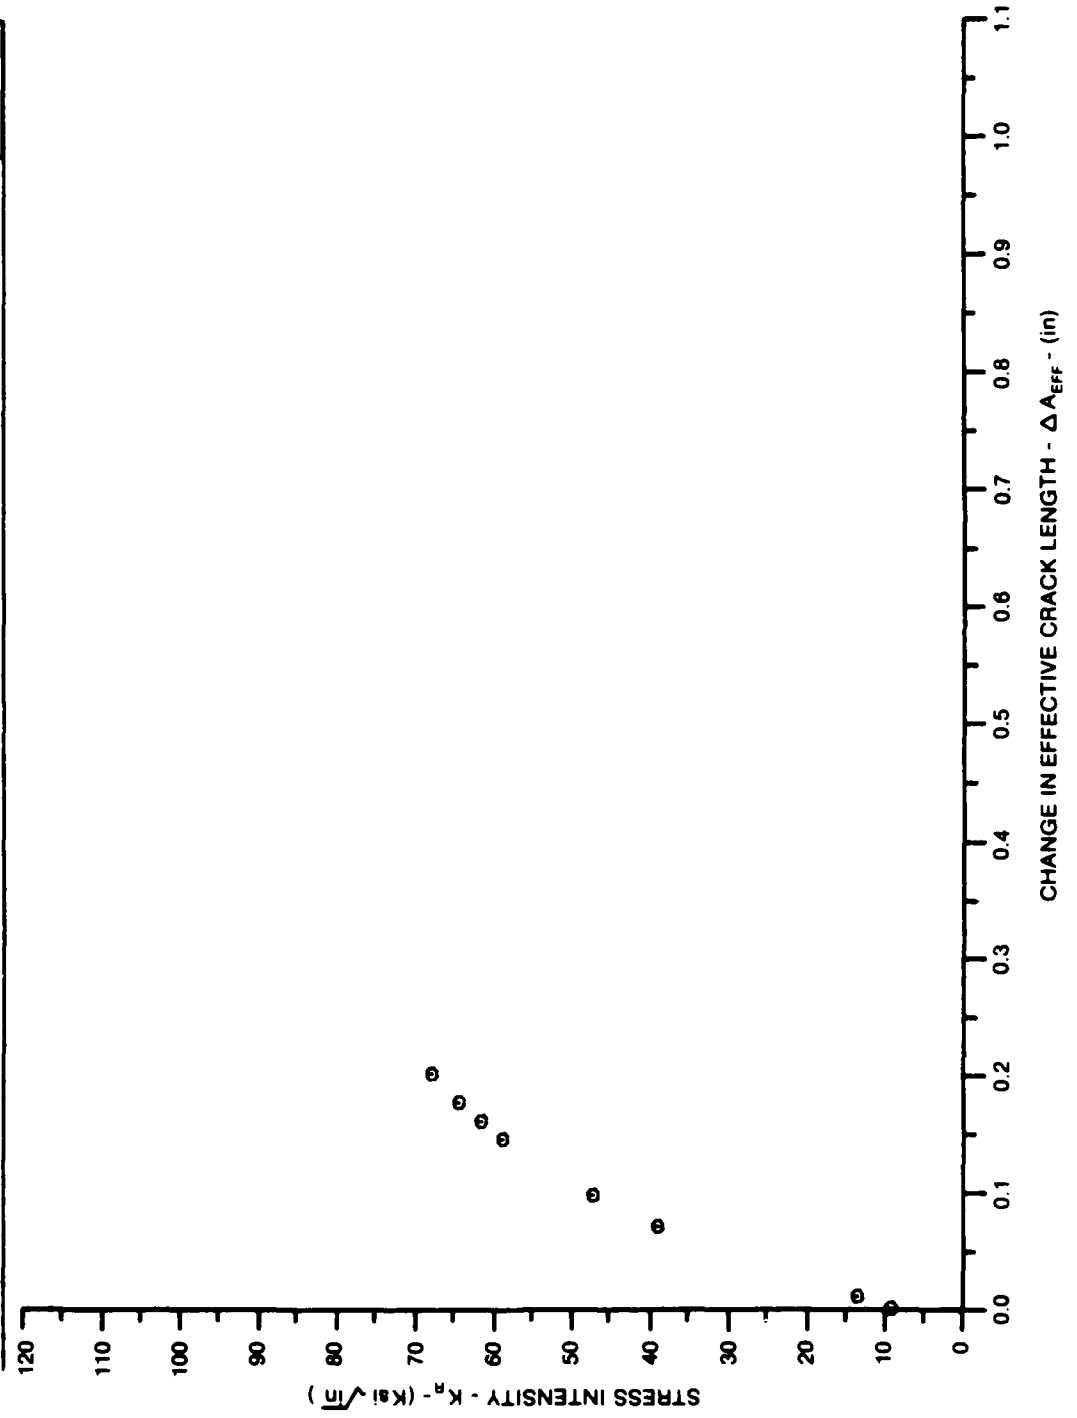


Figure 7.5.2.11

ALUM. ALLOY
2024

SPECIMEN THK: .241"
 SPECIMEN WIDTH: 8.000"
 K_{IC} (Ksi√in):
 REFERENCE: DA001

CONDITION/HT: T351
 FORM: .25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

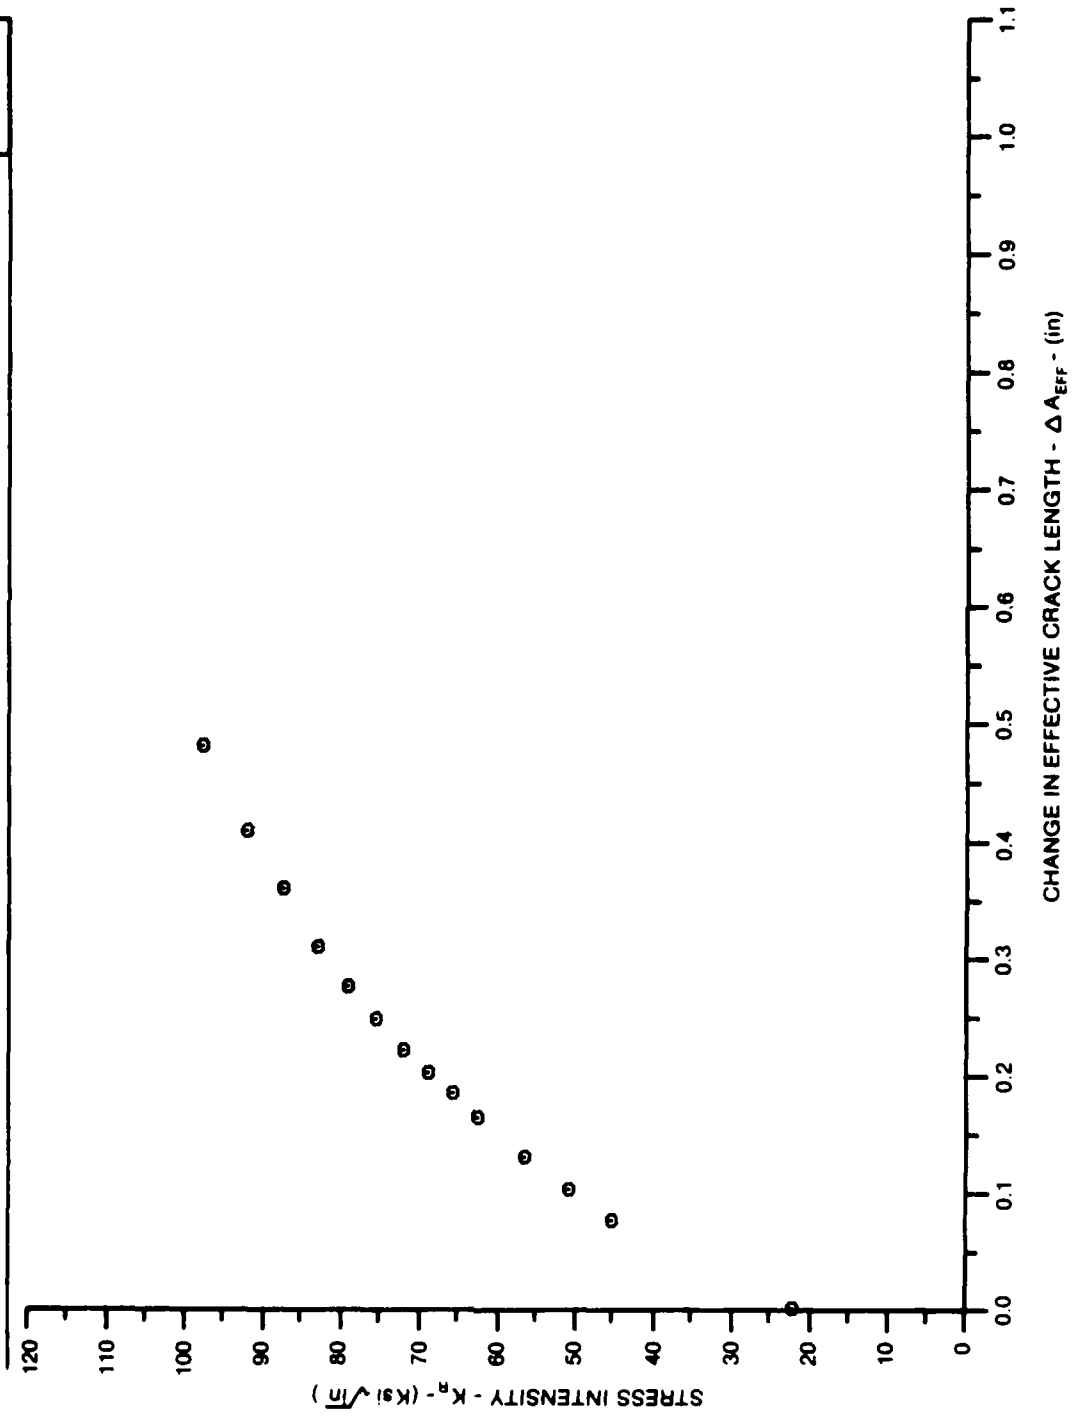


Figure 7.5.2.12

ALUM.
ALLOY

2024

SPECIMEN THK: .241"
SPECIMEN WIDTH: 9.000"
 K_{IC} (KSI \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

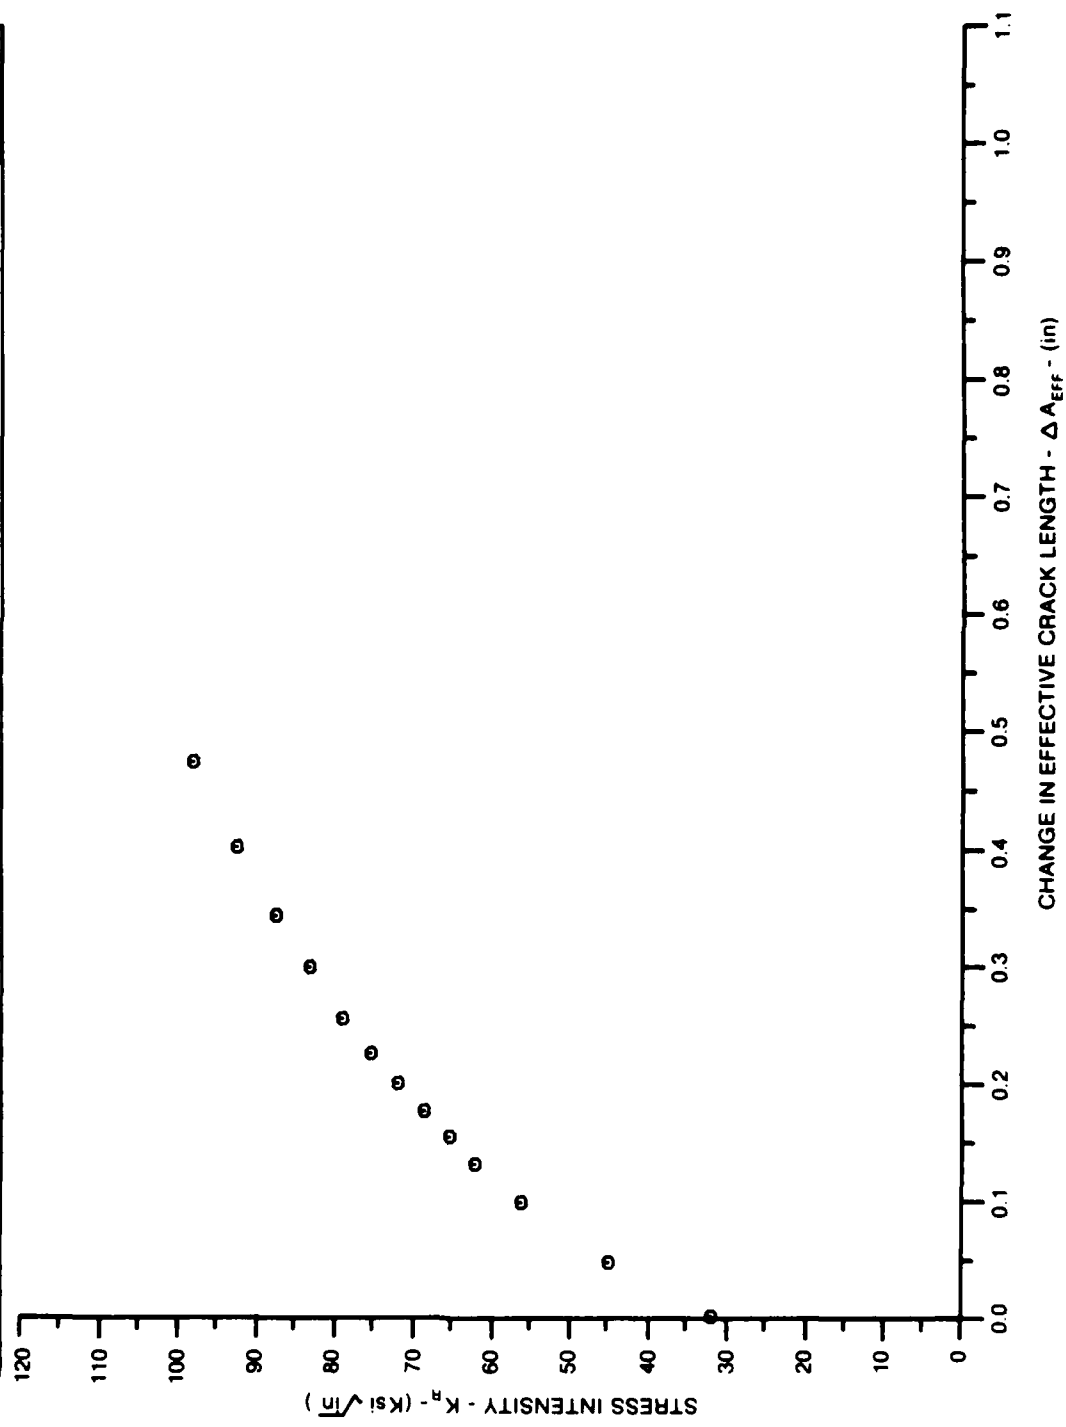


Figure 7.5.2.13

ALUM.
ALLOY

2024

SPECIMEN THK: .241"
SPECIMEN WIDTH: 9.000"
 K_{IC} (Ksi \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

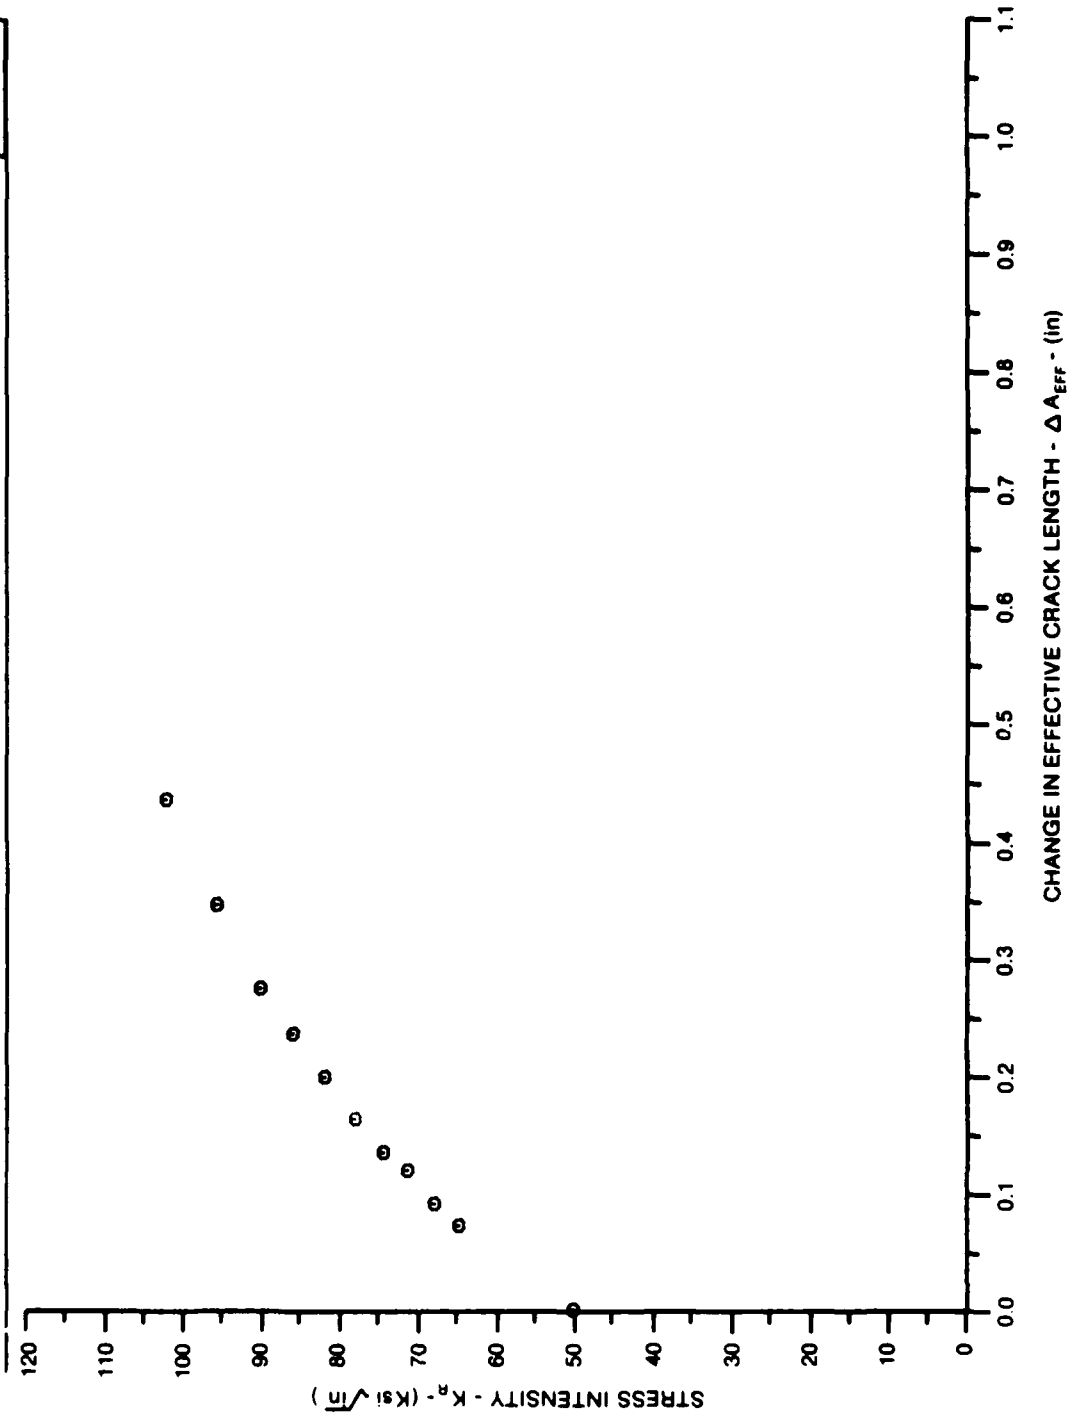


Figure 7.5.2.14

ALUM. ALLOY
2024

SPECIMEN THK: .242"
 SPECIMEN WIDTH: 8.995"
 K_{IC} (Ksi \sqrt{in}):
 REFERENCE: DA001

CONDITION/HT: T351
 FORM: .25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

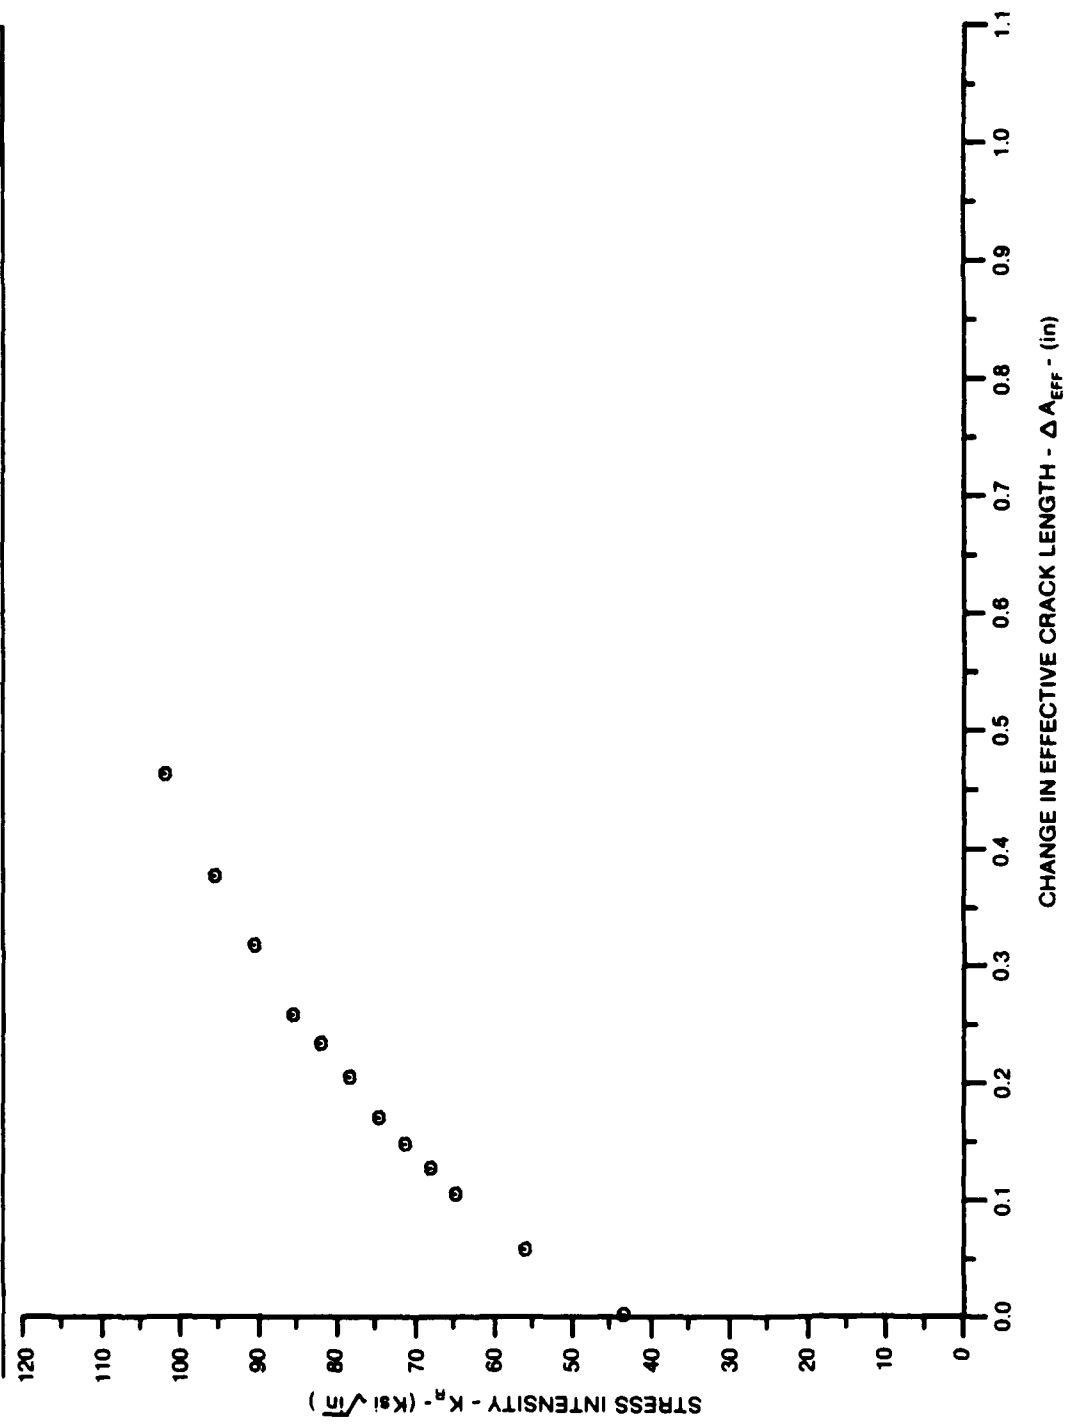


Figure 7.5.2.15

ALUM.
ALLOY

2024

SPECIMEN THK: .242"
SPECIMEN WIDTH: 9.000"
 K_I (Ksi \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

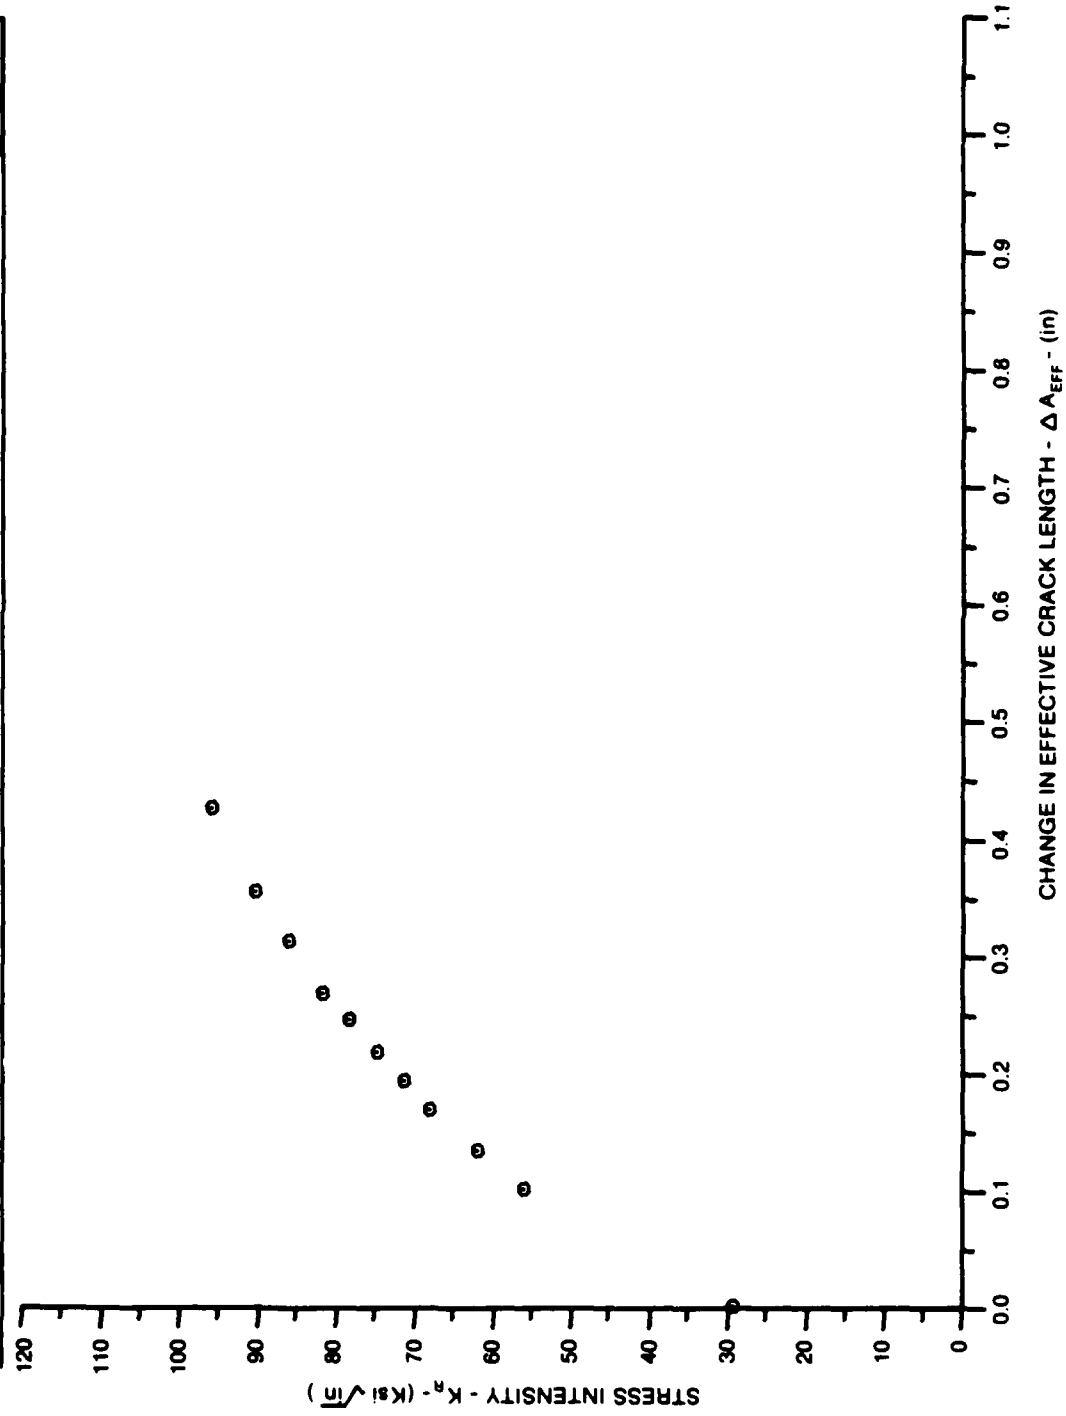


Figure 7.5.2.16

ALUM.
ALLOY

2024

SPECIMEN THK: .250"
SPECIMEN WIDTH: 12.005"
 K_{IC} (Ksi \sqrt{in}):
REFERENCE: DA001

CONDITION/HT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

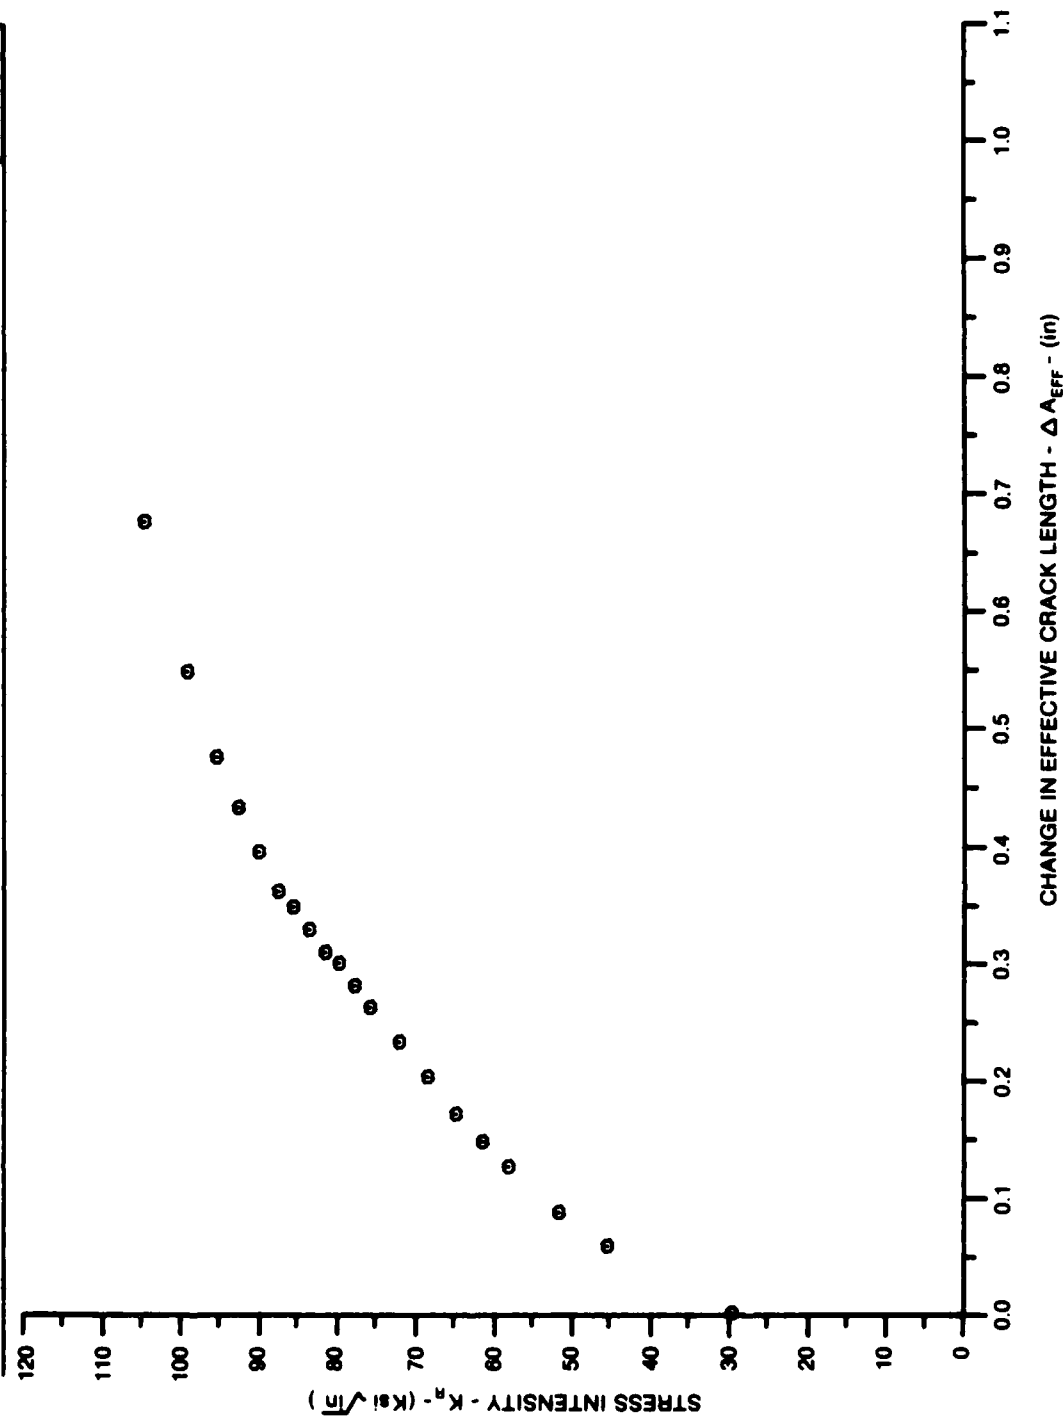


Figure 7.5.2.17

ALUM.
ALLOY

2024

SPECIMEN THK: .250"
SPECIMEN WIDTH: 12.007"
 K_C (ksi \sqrt{in}):
REFERENCE: DA001

CONDITION: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

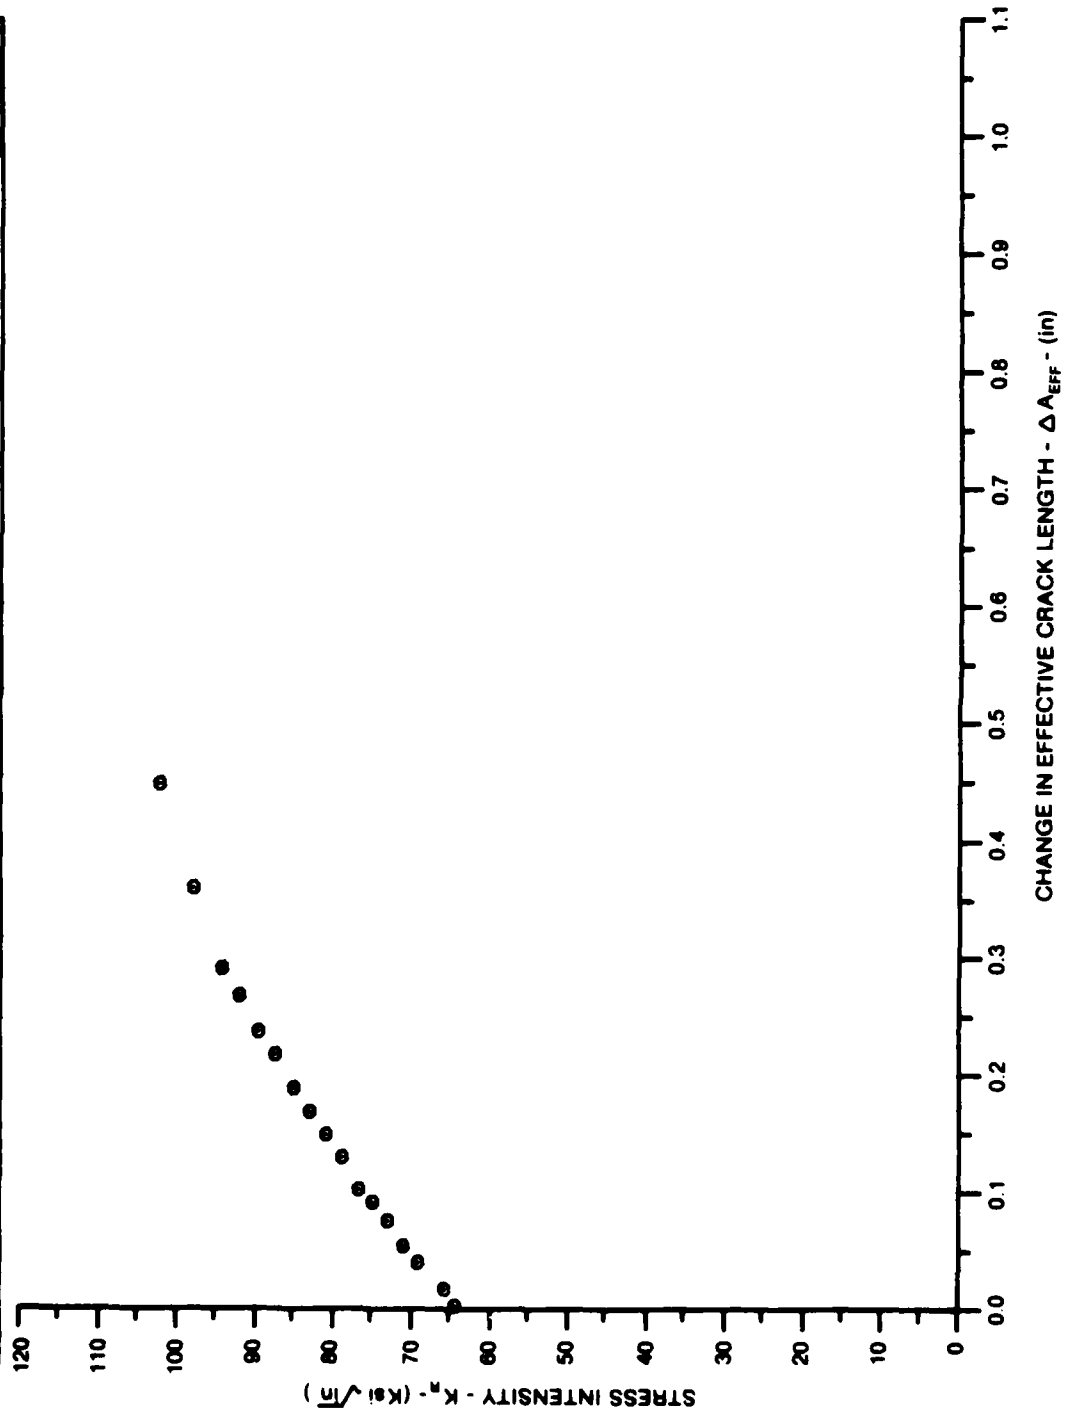


Figure 7.5.2.18

ALUM.
ALLOY

2024

SPECIMEN THK: .260"
SPECIMEN WIDTH: 12.007"
 K_I (Ksi \sqrt{in}):
REFERENCE: DA001

CONDITION/HI: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

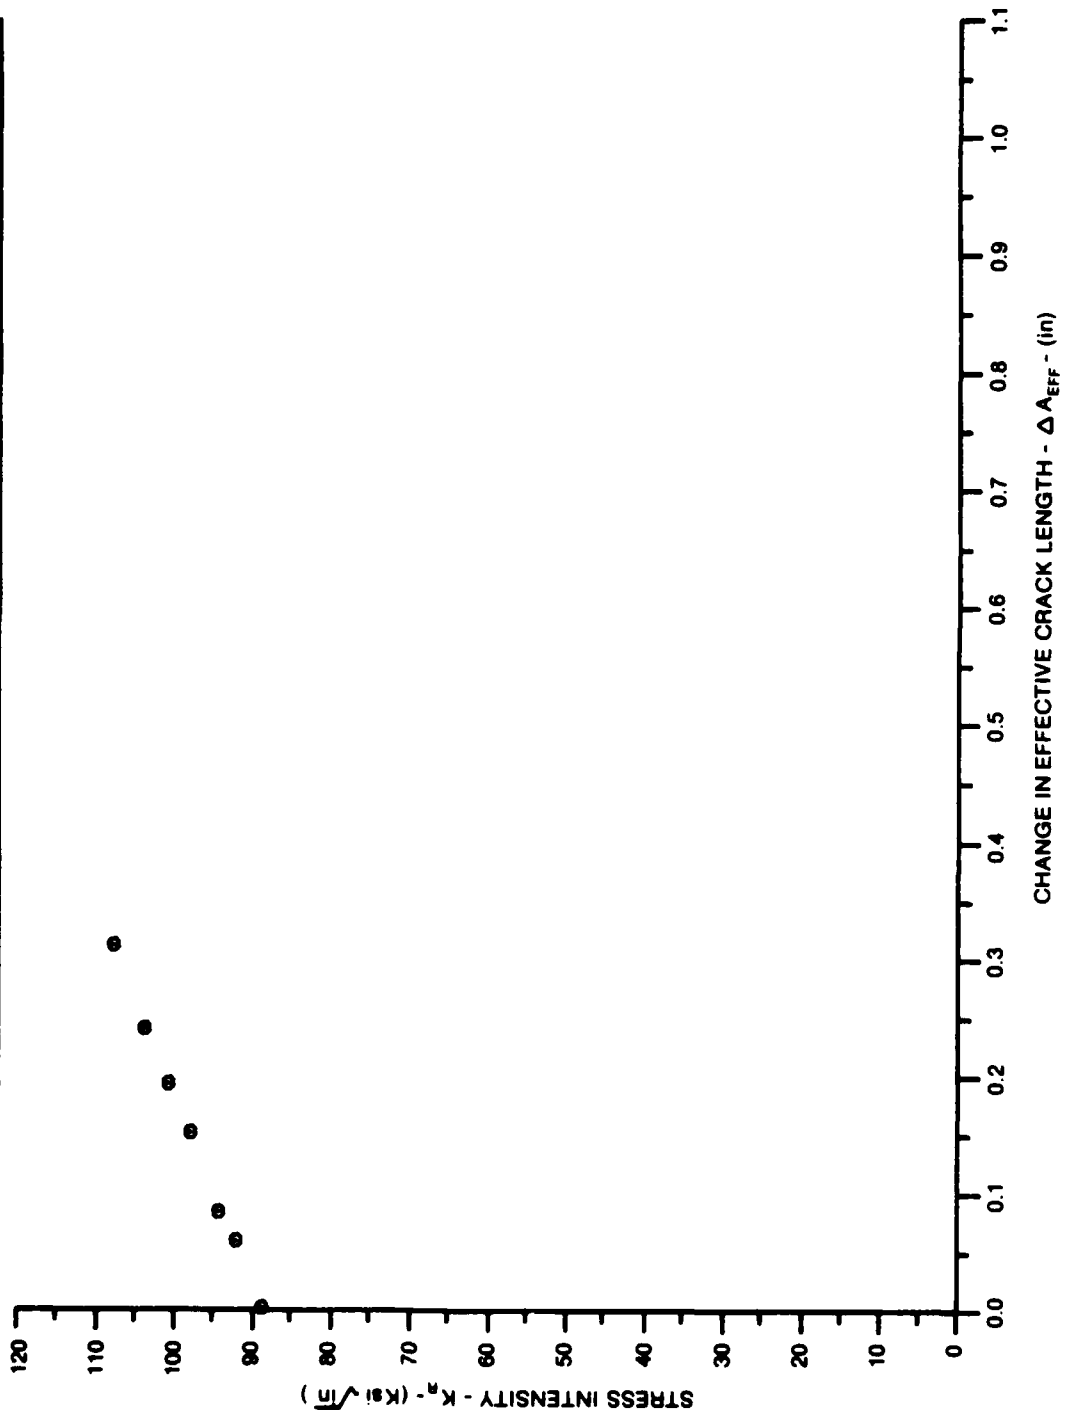


Figure 7.5.2.19

CONDITION/HIT: T351
FORM: .25" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

SPECIMEN THK: .201"
SPECIMEN WIDTH: 12.007"
 K_{IC} (ksi \sqrt{in}):
REFERENCE: DA001

ALUM.
ALLOY

2024

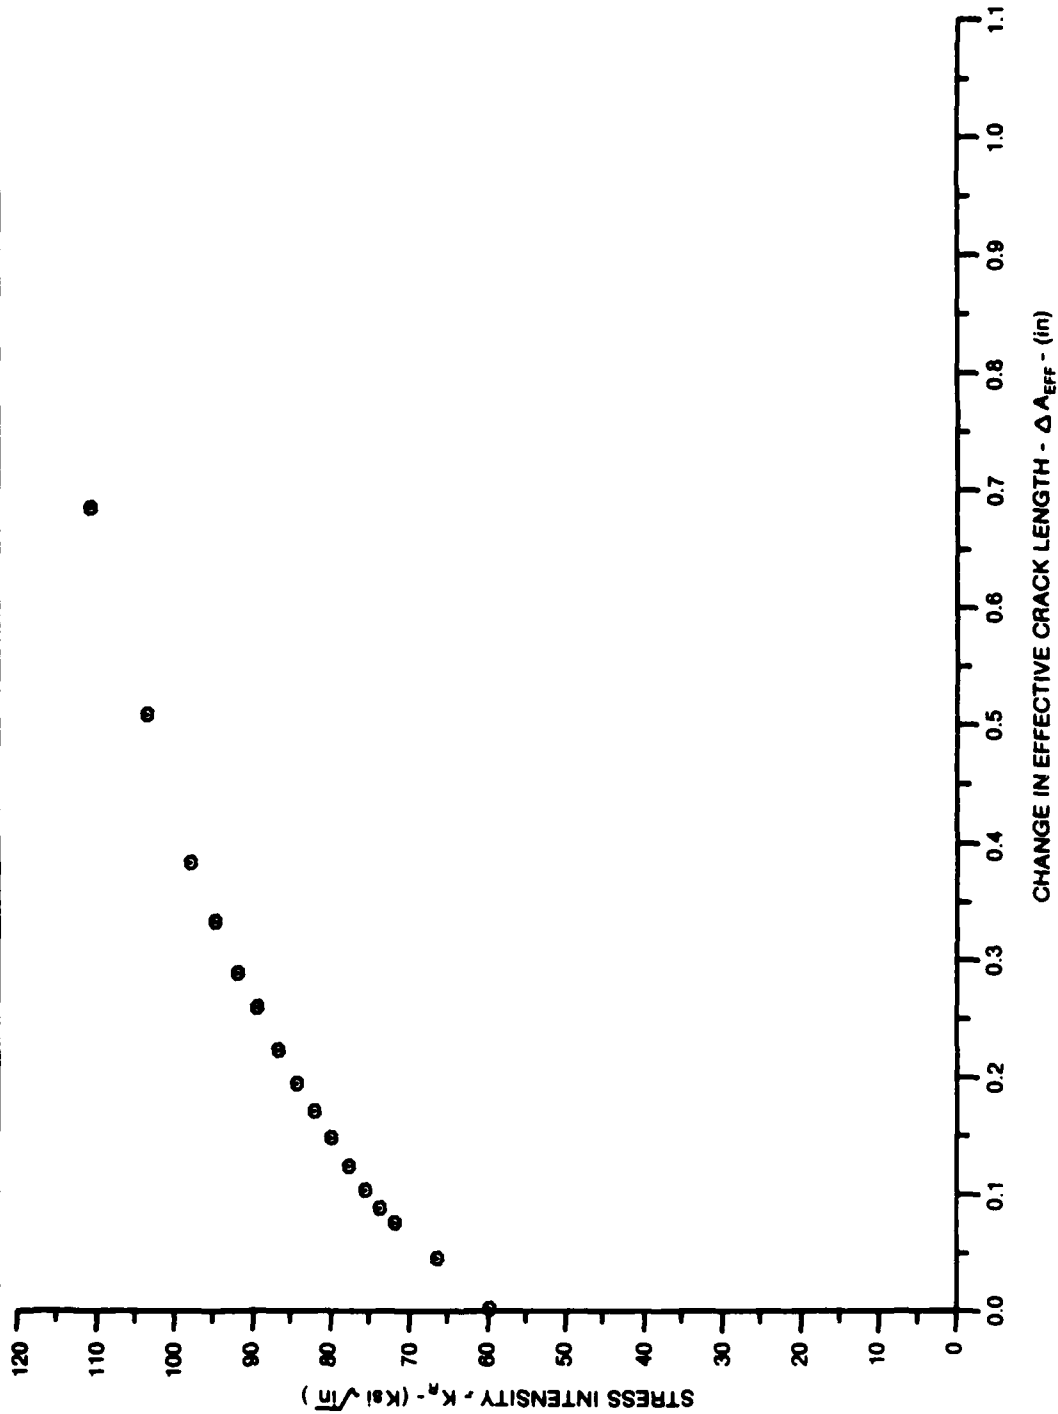


Figure 7.5.2.20

ALUM.
ALLOY

2024

SPECIMEN THK: .120"
SPECIMEN WIDTH: 5.988"
 K_{IC} (Ksi√in): 91.8
REFERENCE: G0005

CONDITION/HT: T62 (GG)
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

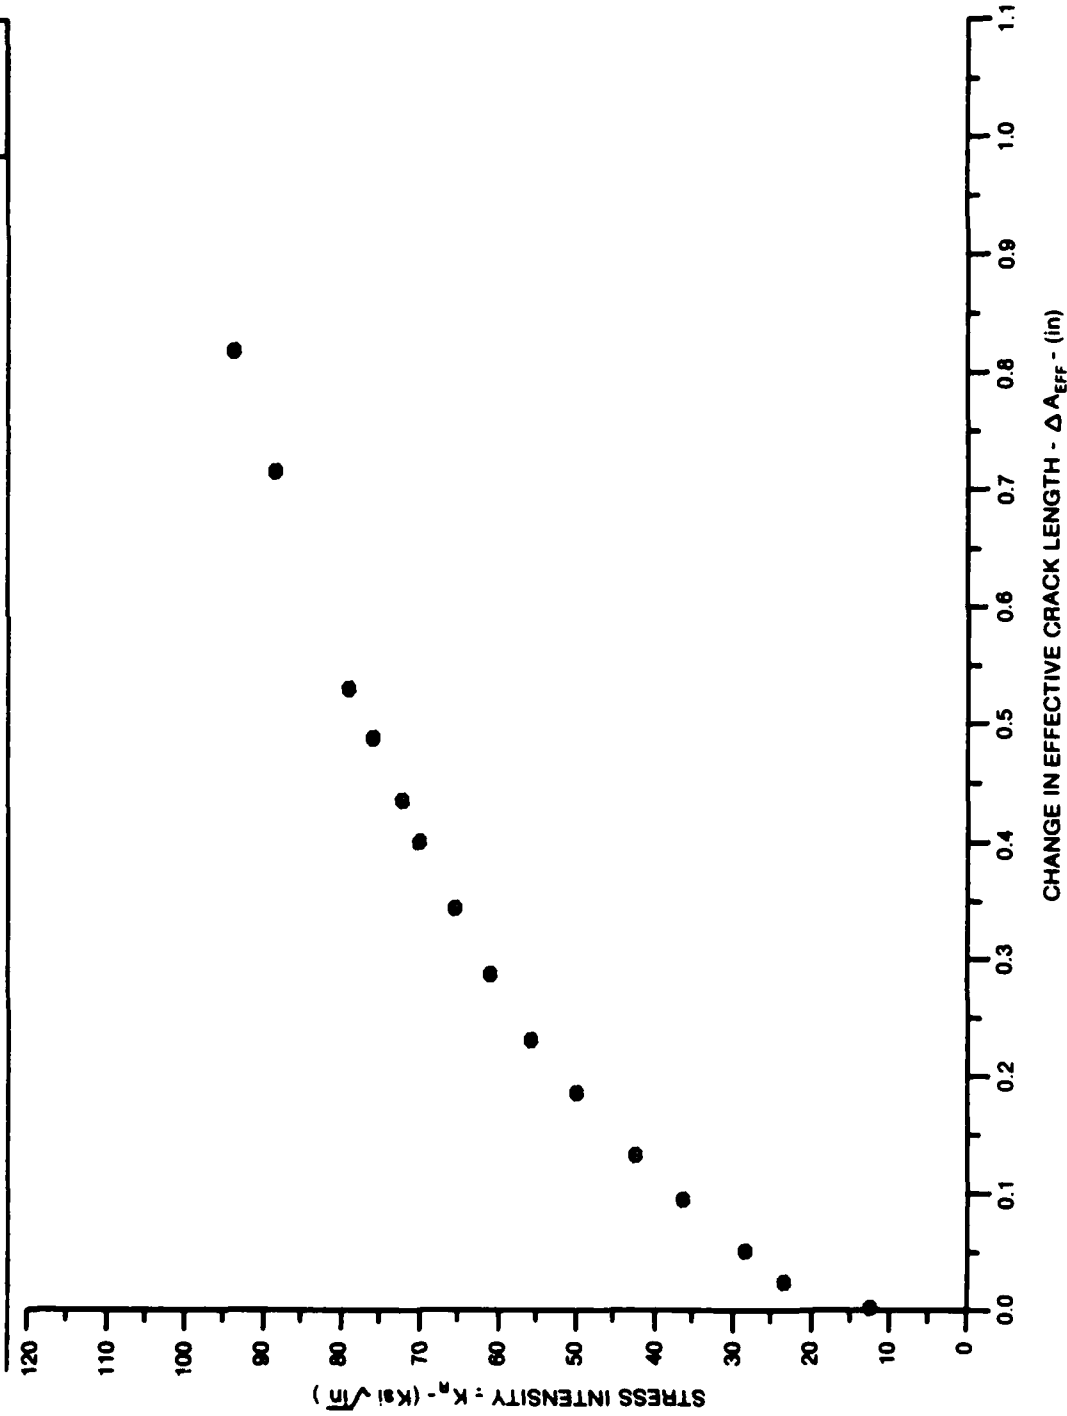


Figure 7.5.2.21

ALUM.
ALLOY

2024

SPECIMEN THK: .128"
SPECIMEN WIDTH: 15.978"
 K_{Ic} (Ksi \sqrt{in}): 80.0
REFERENCE: GD005

CONDITION/HT: T02 (G0)
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

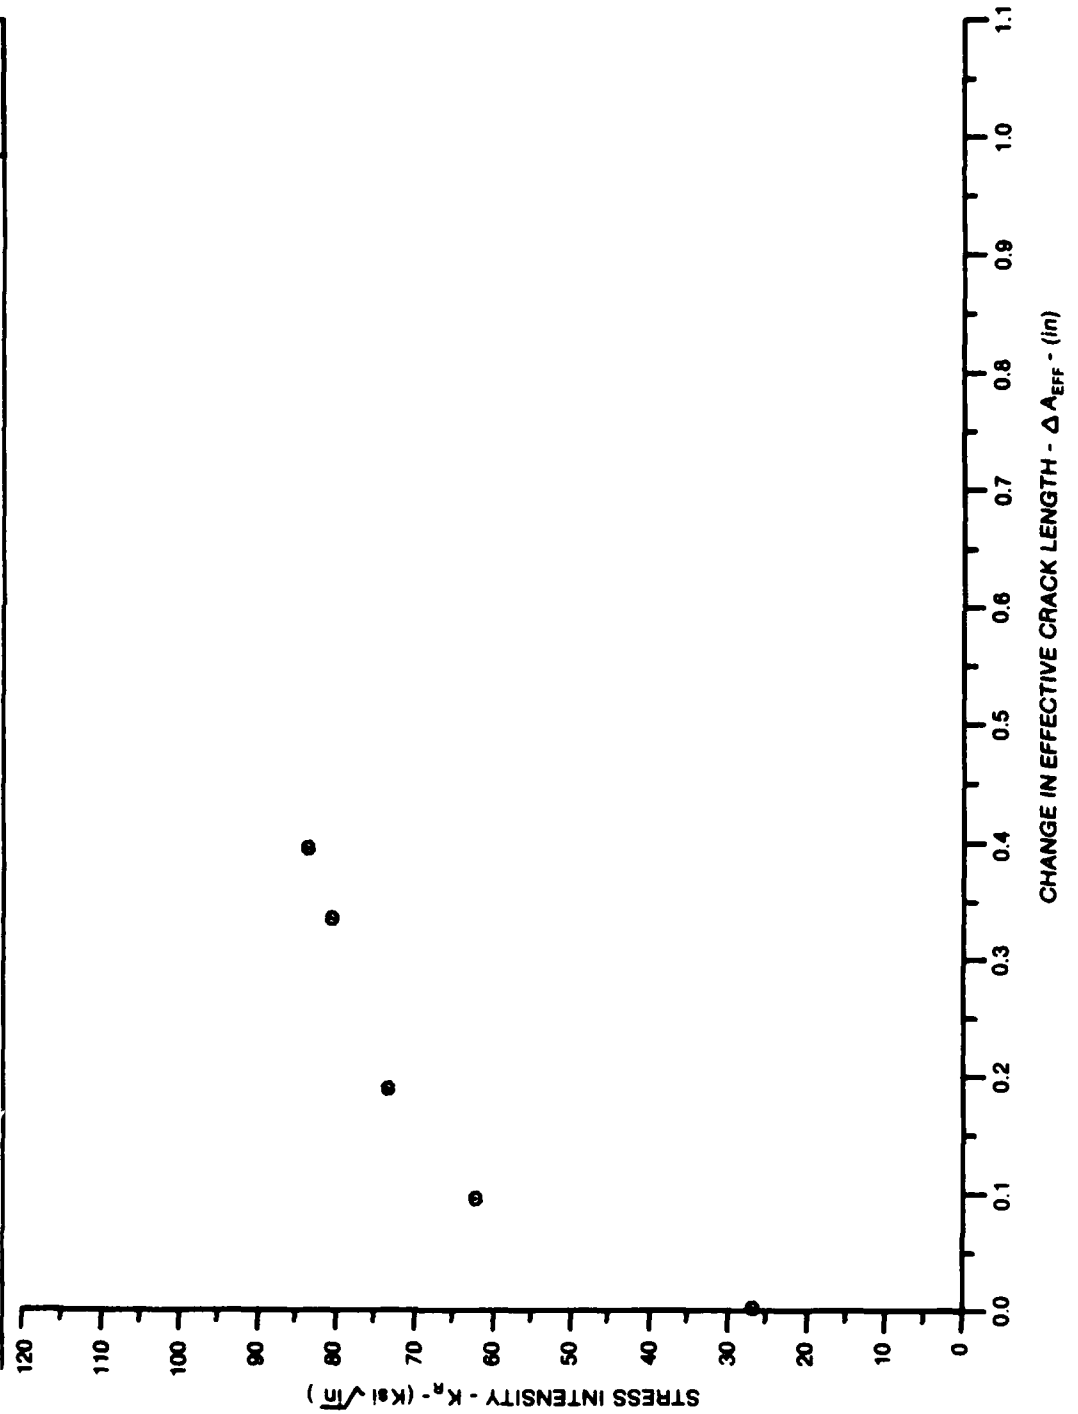


Figure 7.5.2.22

ALUM.
ALLOY

2024

SPECIMEN THK: .128"
SPECIMEN WIDTH: 10.000"
K_c (Ksi√in): 136.0
REFERENCE: GD005

CONDITION: T62 (GD)
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

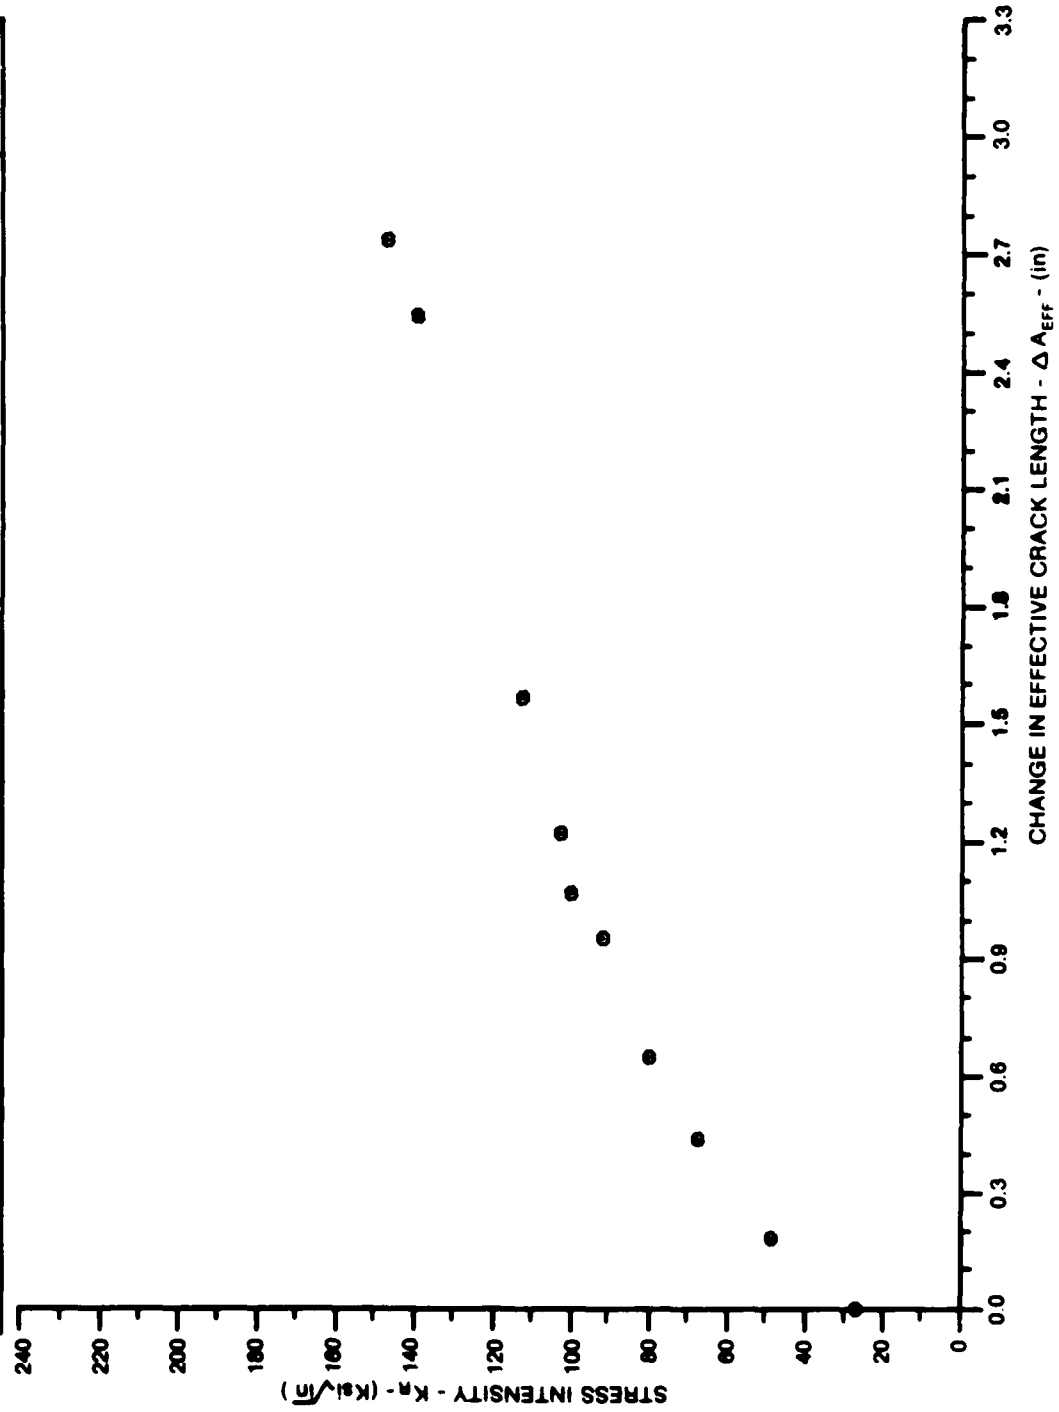


Figure 7.5.2.23

ALUM.
ALLOY

2024

SPECIMEN THK: .125"
SPECIMEN WIDTH: 5.998"
 K_{IC} (KSI \sqrt{in}): 62.0
REFERENCE: GD005

CONDITION/HT: T02 (G0)
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: T-L

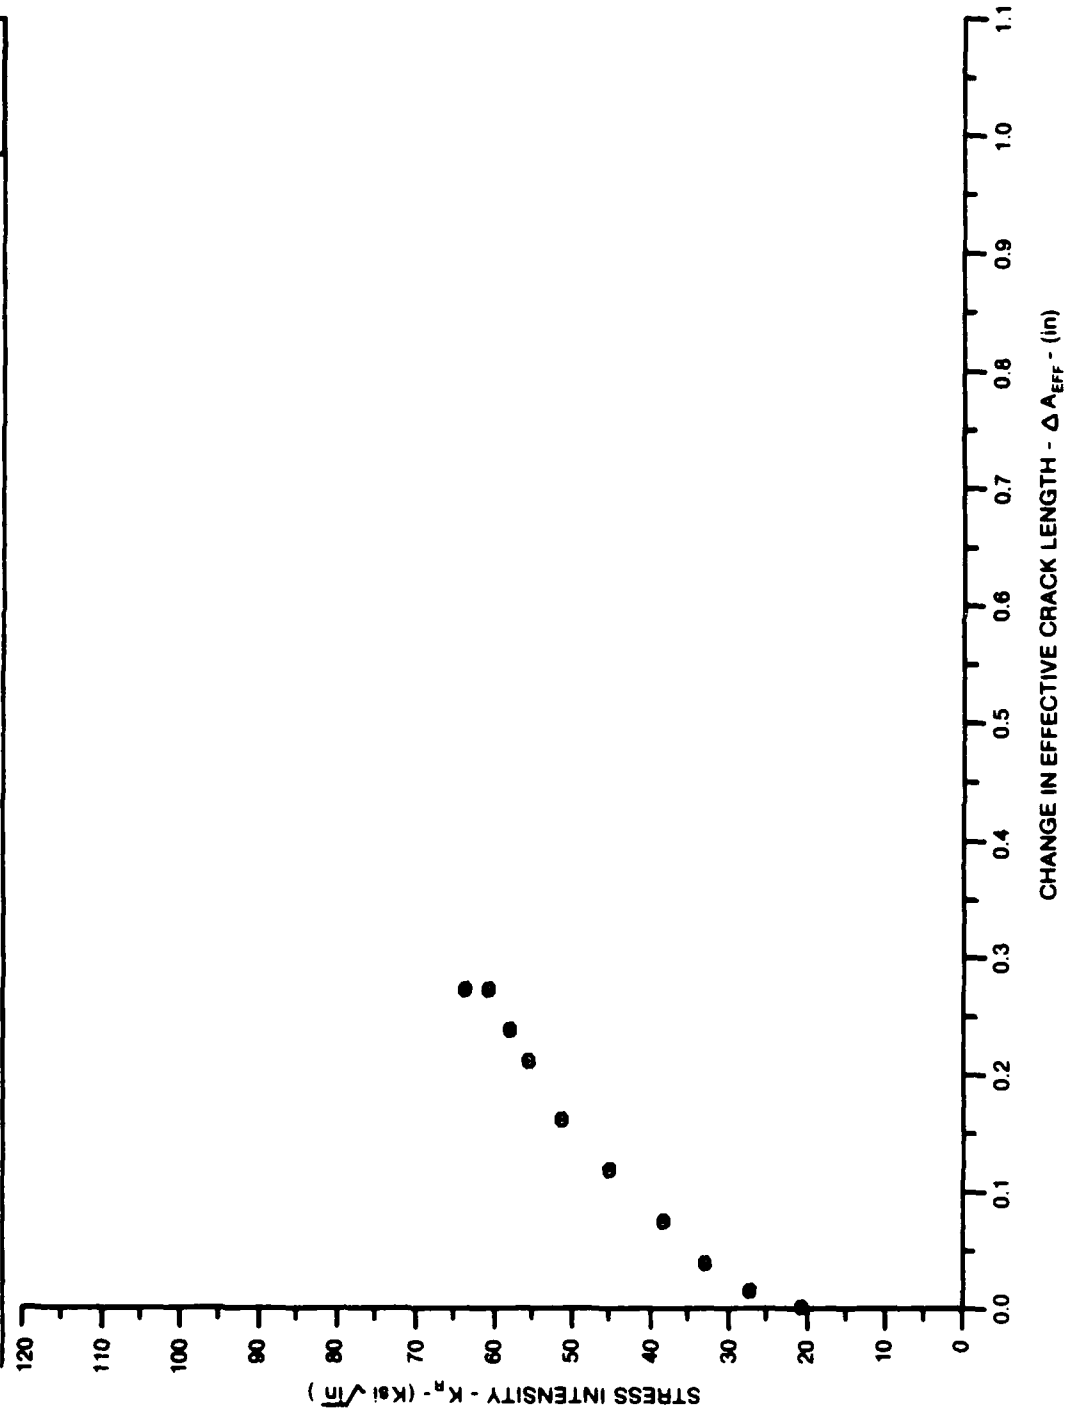


Figure 7.5.2.24

ALUM.
ALLOY

2024

SPECIMEN THK: .125"
 SPECIMEN WIDTH: 5.000"
 K_{IC} (KSI \sqrt{in}): 84.8
 REFERENCE: G0005

CONDITION/HT: T62 (GD)
 FORM: .13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L

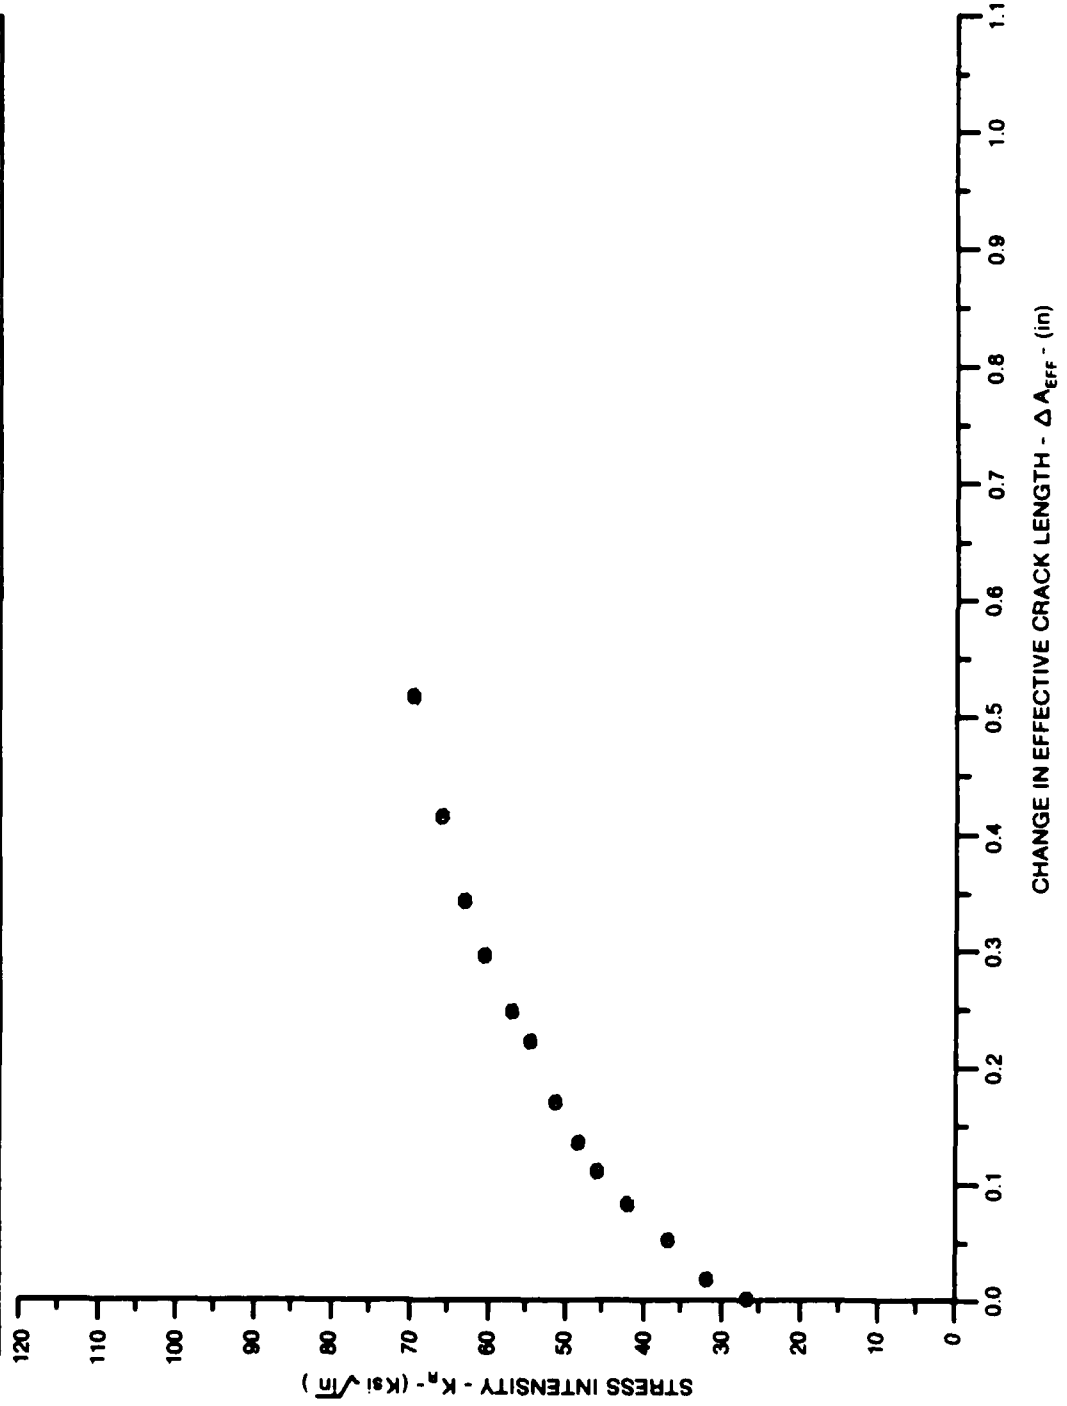


Figure 7.5.2.25

ALUM.
ALLOY

2024

SPECIMEN THK: .126"
SPECIMEN WIDTH: 6.000"
 K_{IC} (Ksi \sqrt{in}): 74.0
REFERENCE: GD005

CONDITION/HT: T62 (ND)
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

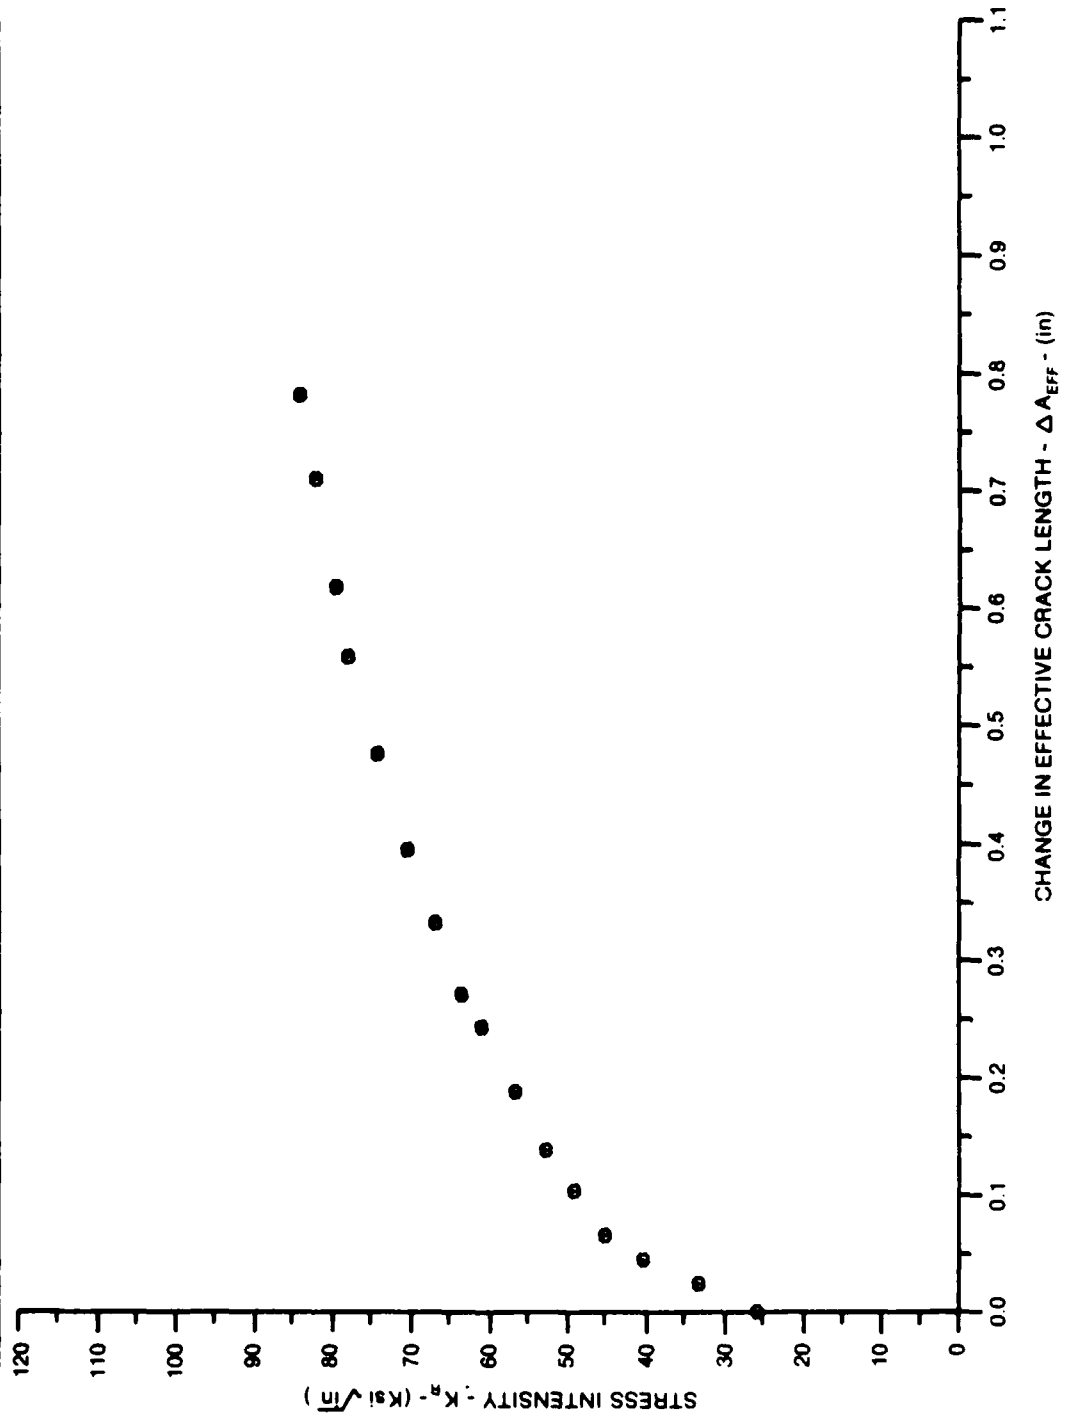


Figure 7.5.2.26

ALUM.
ALLOY

2024

SPECIMEN THK: .128"
 SPECIMEN WIDTH: 5.088"
 K_I (kg/ \sqrt{m}): 79.8
 REFERENCE: CD885

CONDITION/HT: T62 (VD)
 FORM: .13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

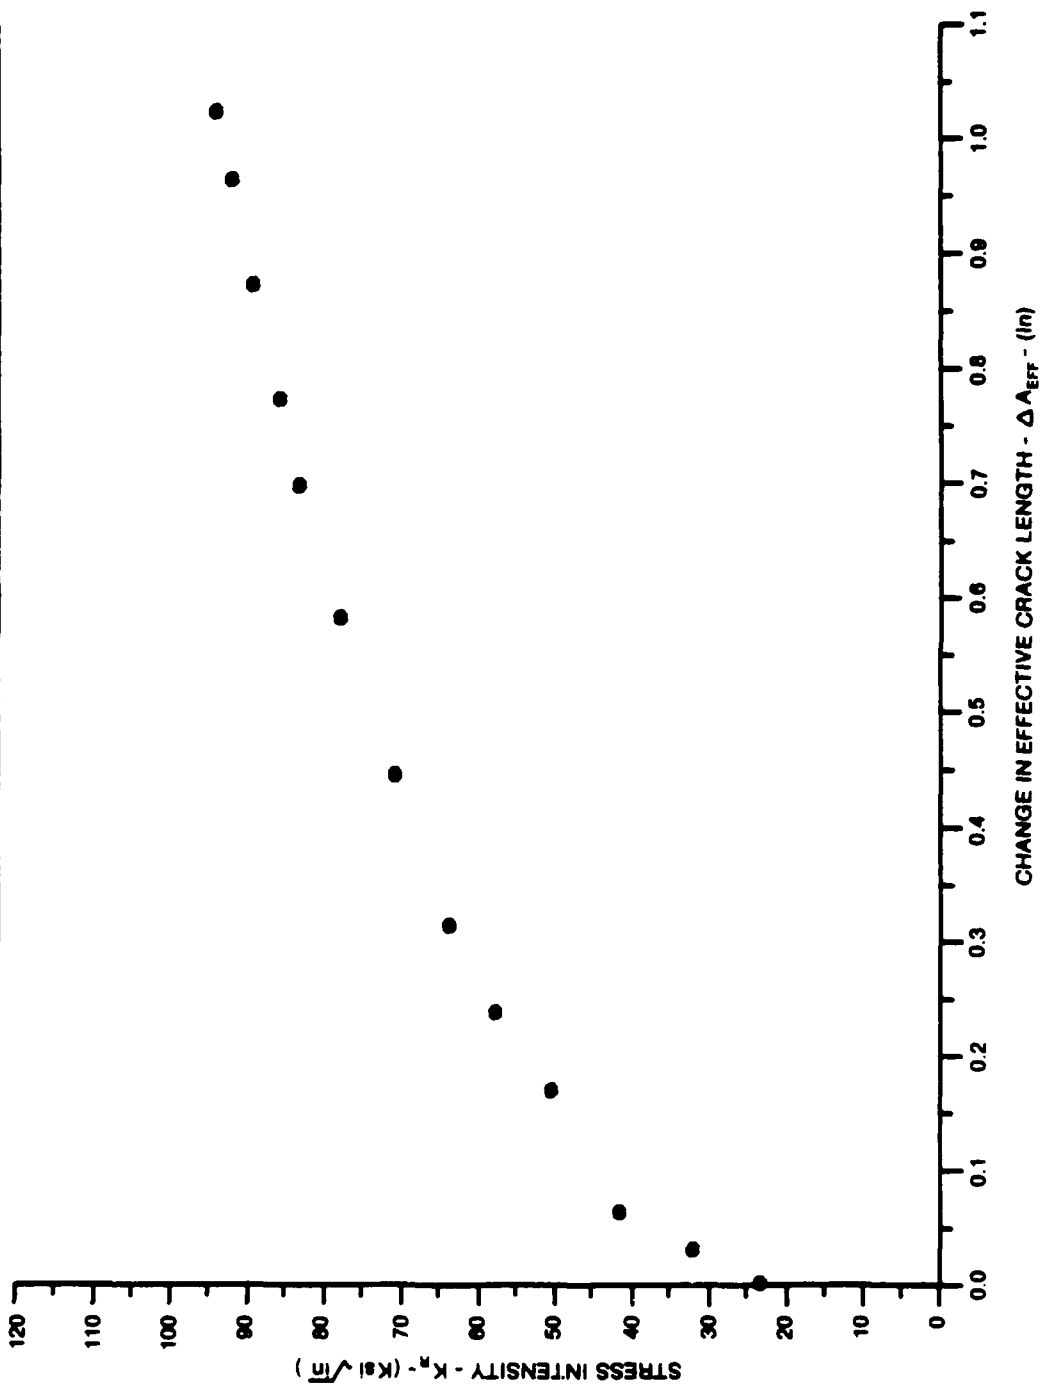


Figure 7.5.2.27

ALUM.
ALLOY

2024

SPECIMEN THK: .126"
SPECIMEN WIDTH: 15.988"
 $K_I(Ksi\sqrt{in})$: 138.0
REFERENCE: GD005

CONDITION/HT: T62 (WQ)
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

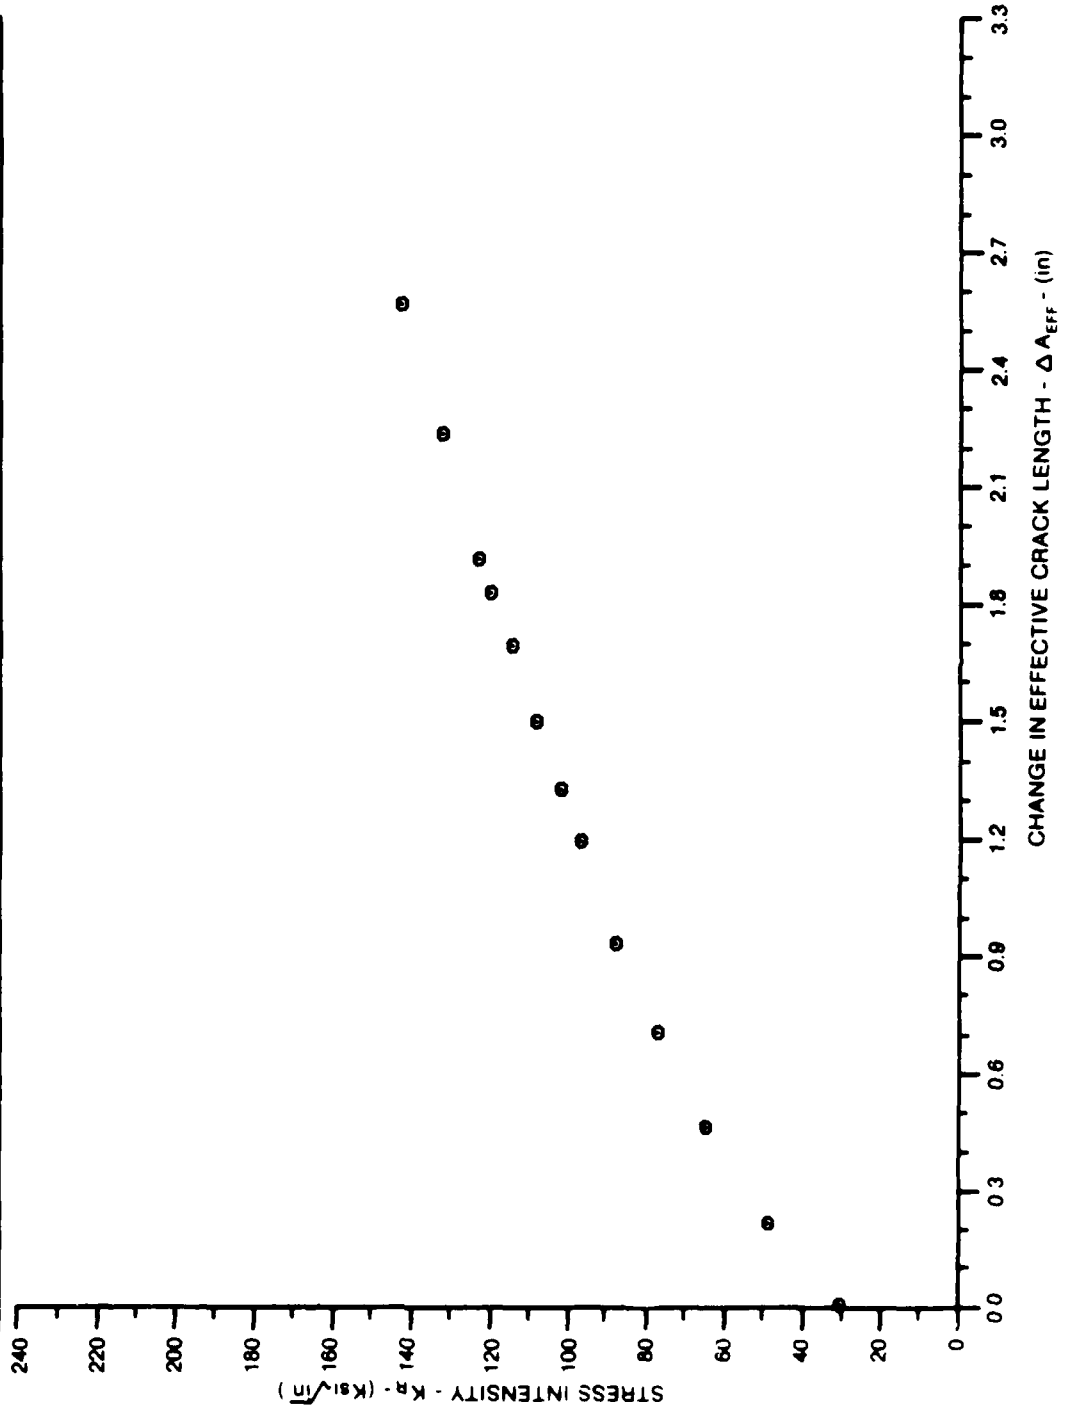


Figure 7.1.1.2.2

ALUM.
ALLOY

2024

SPECIMEN THK: .126"
SPECIMEN WIDTH: 5.988"
 K_{IC} (Ksi \sqrt{in}): 70.9
REFERENCE: G0005

CONDITION/HT: T62 (WQ)
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: T-L

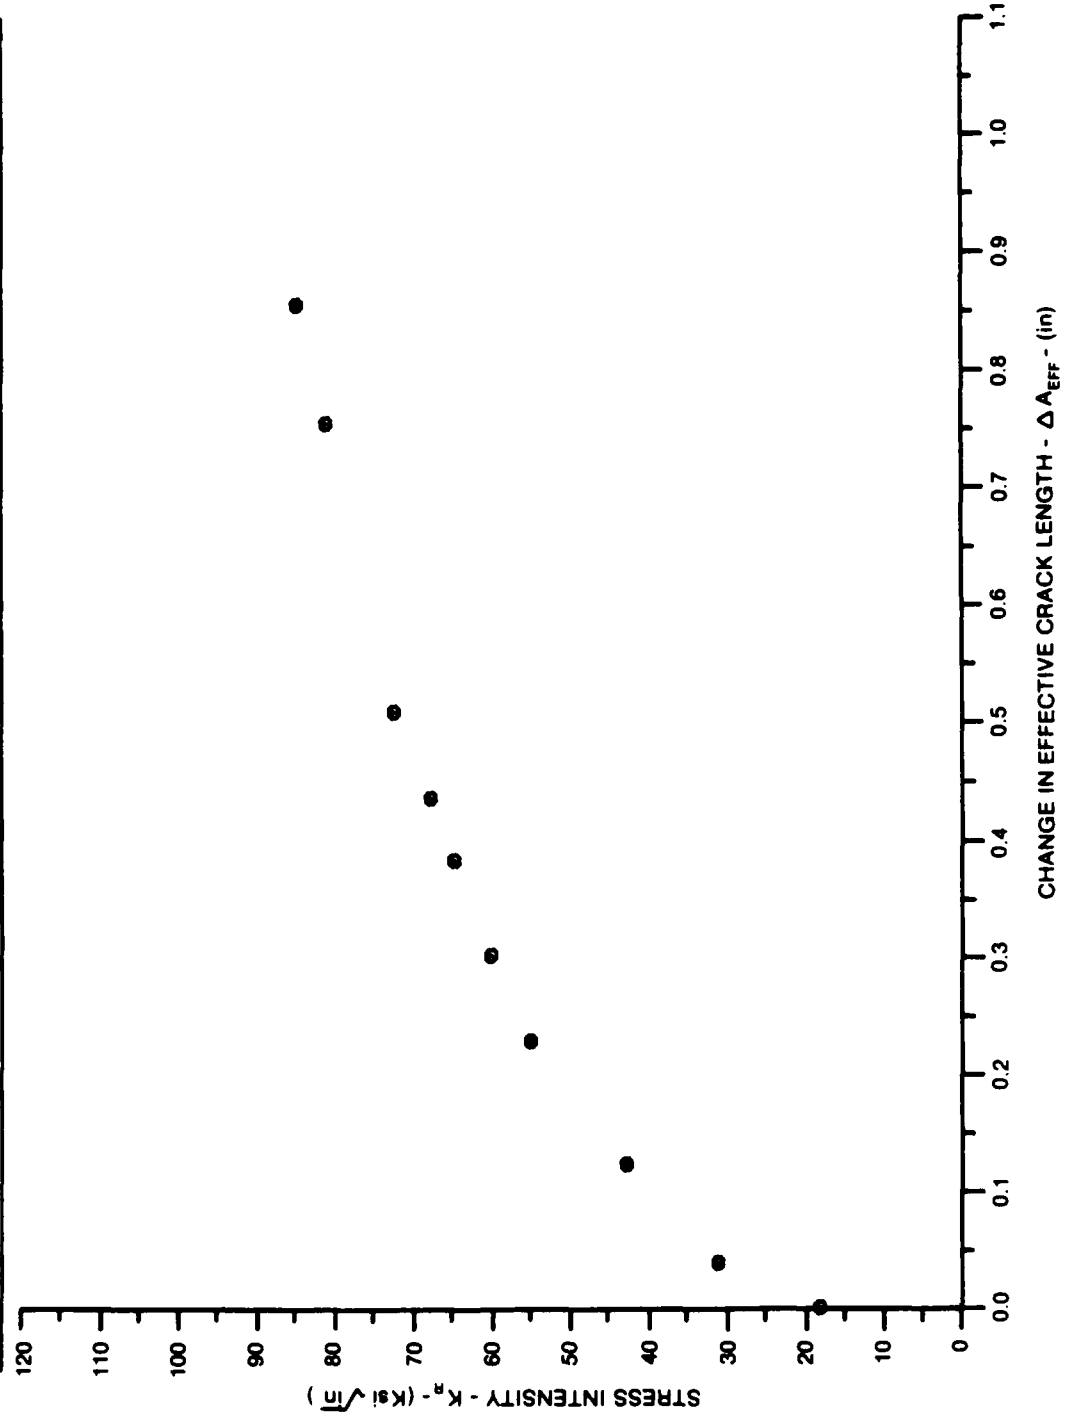


Figure 7.5.2.29

ALUM.
ALLOY

2024

SPECIMEN THK: .125"
 SPECIMEN WIDTH: 5.000"
 K_C (KSI \sqrt{in}): 73.6
 REFERENCE: G0005

CONDITION/HT: T62 (ND)
 FORM: .13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L

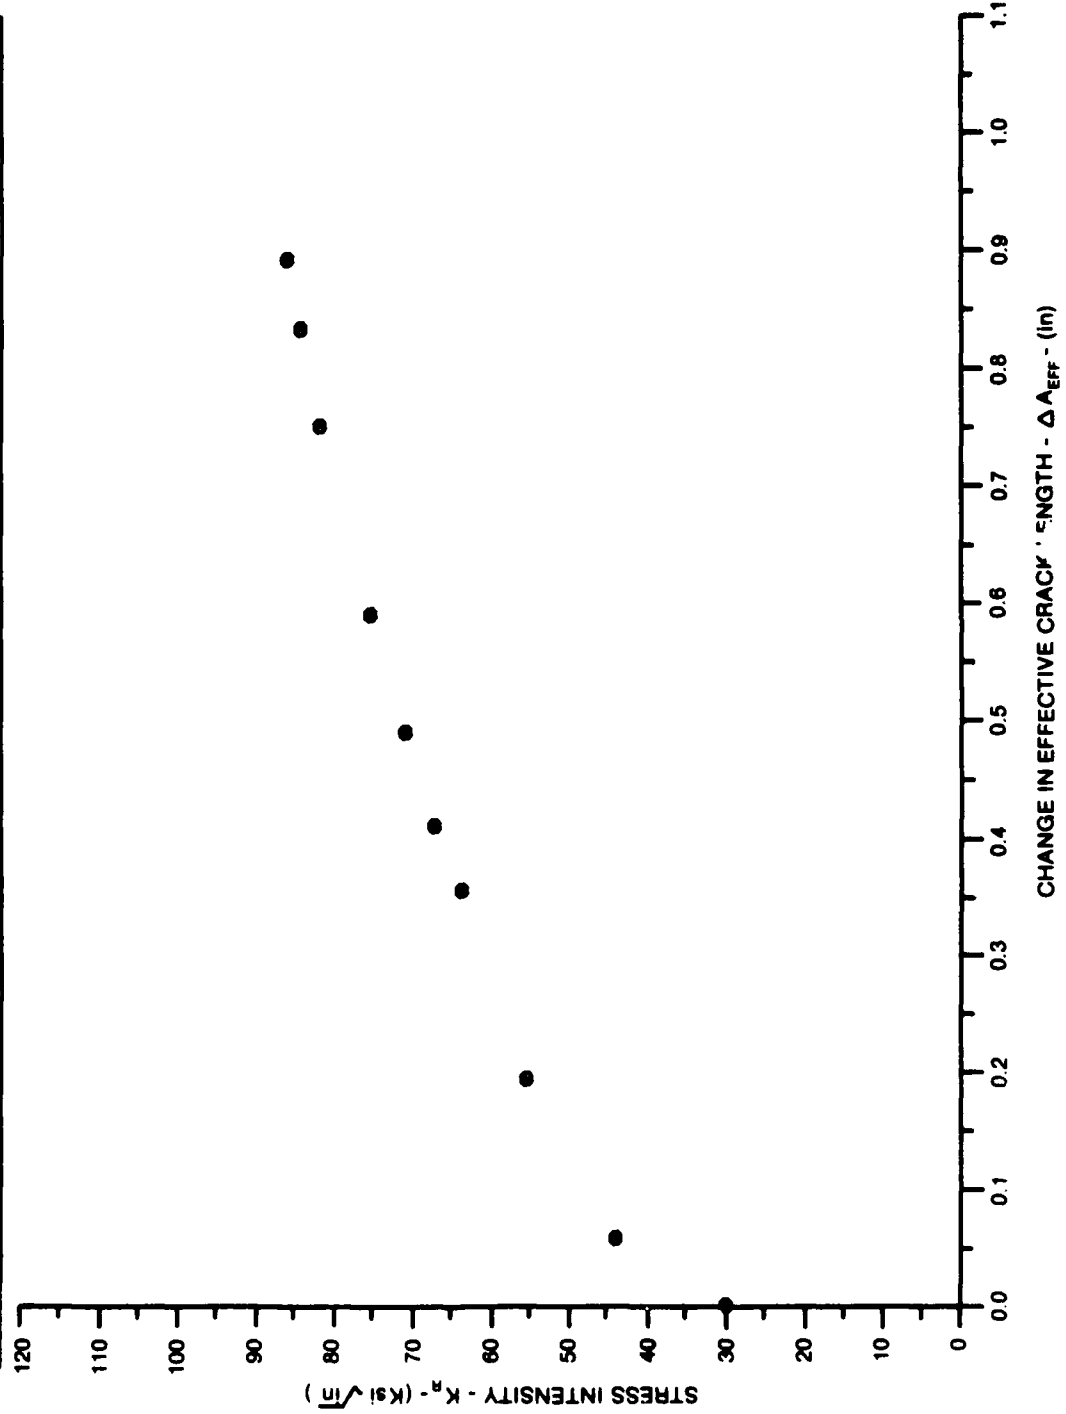


Figure 7.5.2.30

ALUM.
ALLOY

2024

CONDITION/HT: T81
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

SPECIMEN THK: .125"
SPECIMEN WIDTH: 5.988"
 K_{IC} (Ksi \sqrt{in}): 83.1
REFERENCE: GDB05

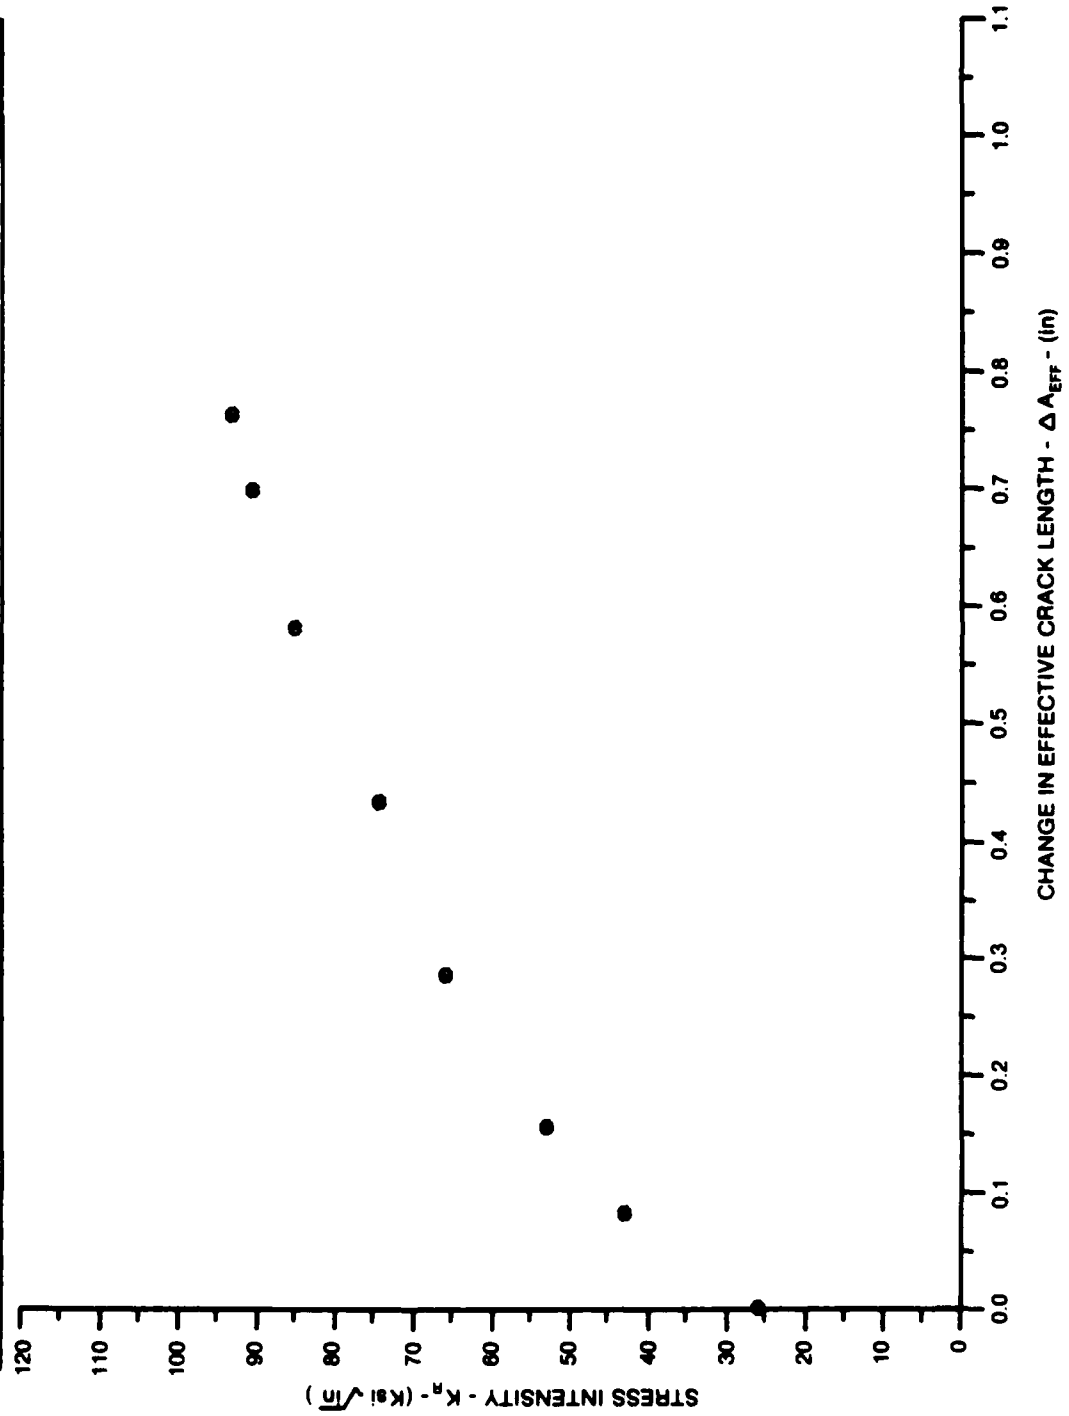


Figure 7.5.2.31

ALUM. ALLOY
2024

SPECIMEN THK: .126"
 SPECIMEN WIDTH: 5.990"
 K_C (ksi \sqrt{in}): 62.6
 REFERENCE: GD005

CONDITION/HT: T81
 FORM: .13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

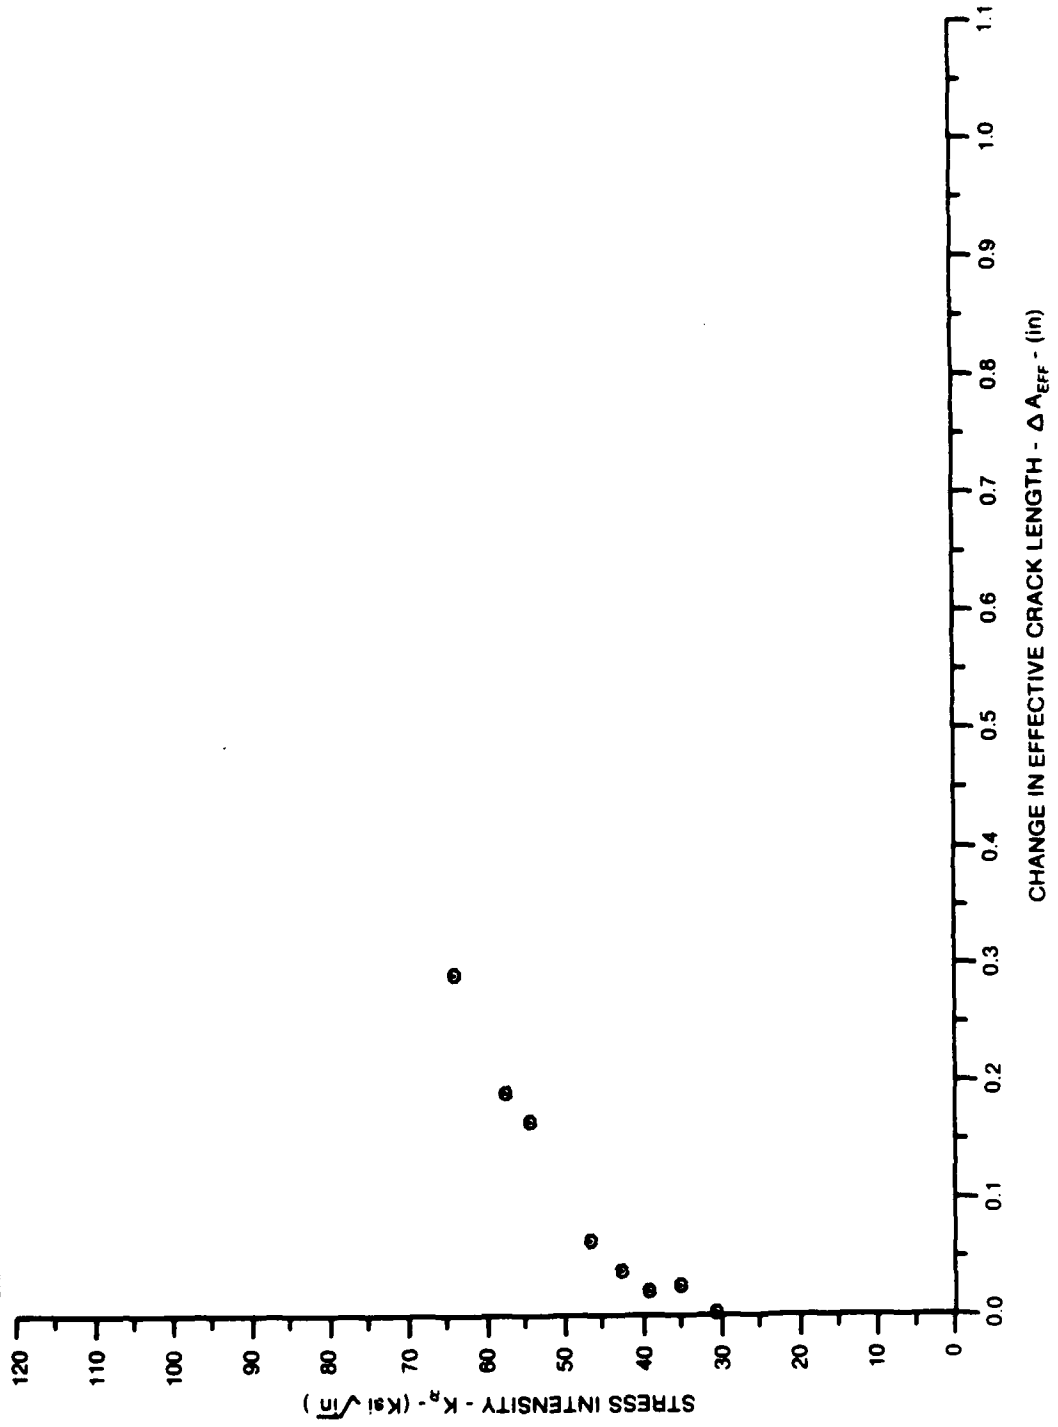


Figure 7.5.2.32

CONDITION/HT: T81
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

SPECIMEN THK: .128"
SPECIMEN WIDTH: 5.998"
 K_C (KSI \sqrt{in}): 68.0
REFERENCE: GD885

ALUM.
ALLOY
2024

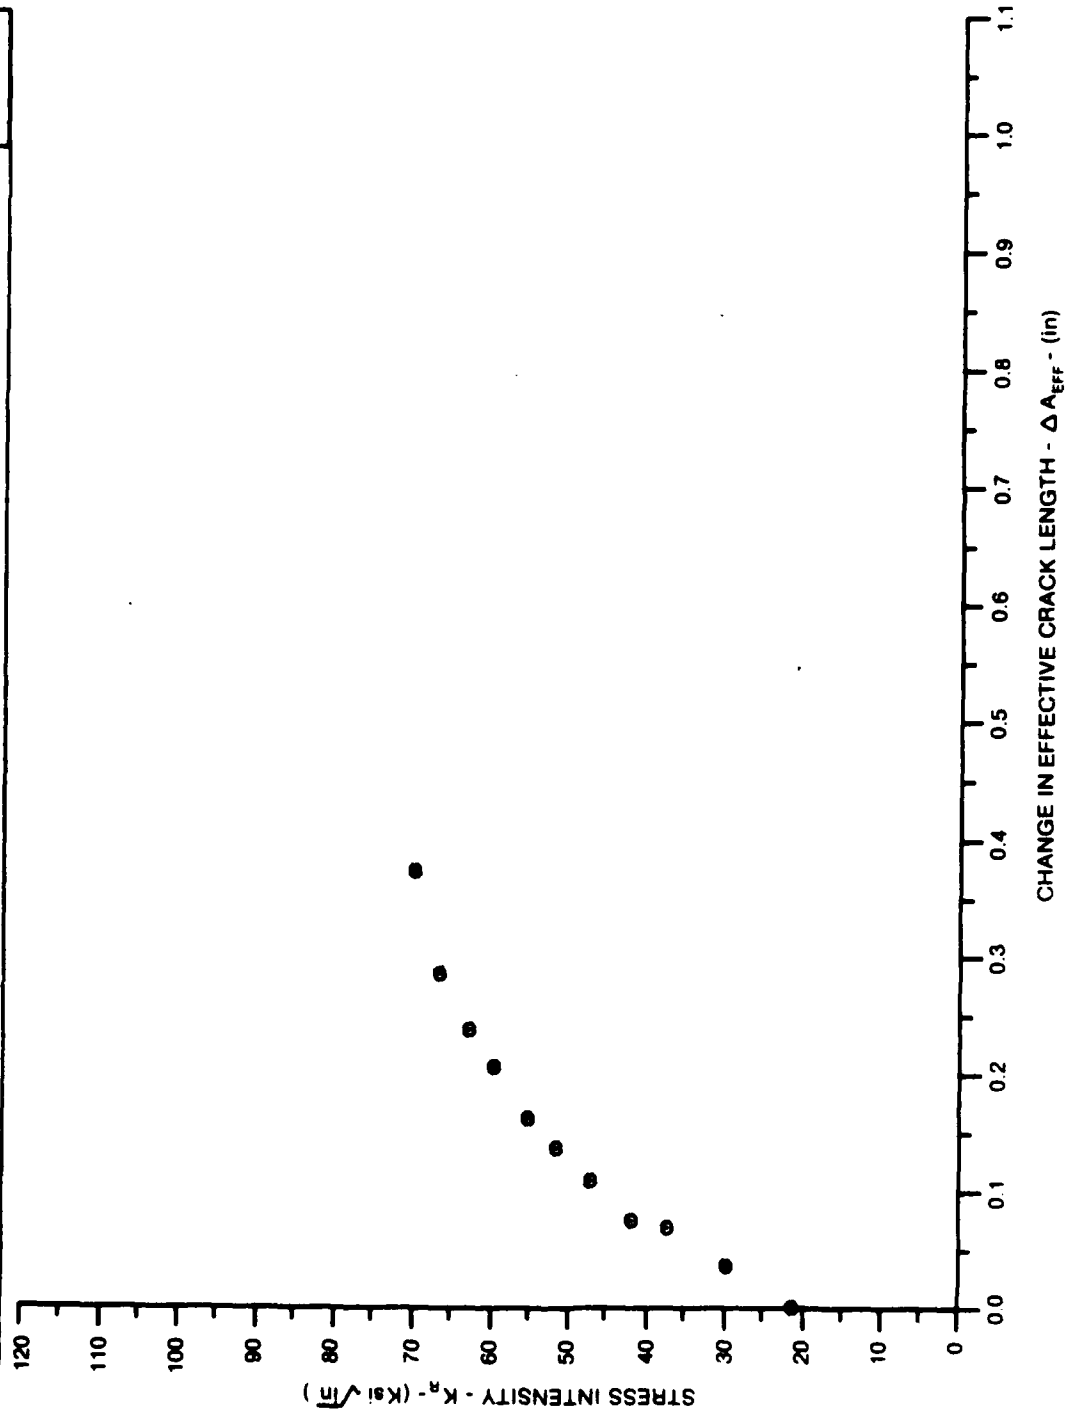


Figure 7.5.2.33

ALUM.
ALLOY

2024

SPECIMEN THK: .126"
SPECIMEN WIDTH: 5.000"
 K_{IC} (ksi√in): 50.8
REFERENCE: G0005

CONDITION/T: T01
FORM: .13" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: T-L

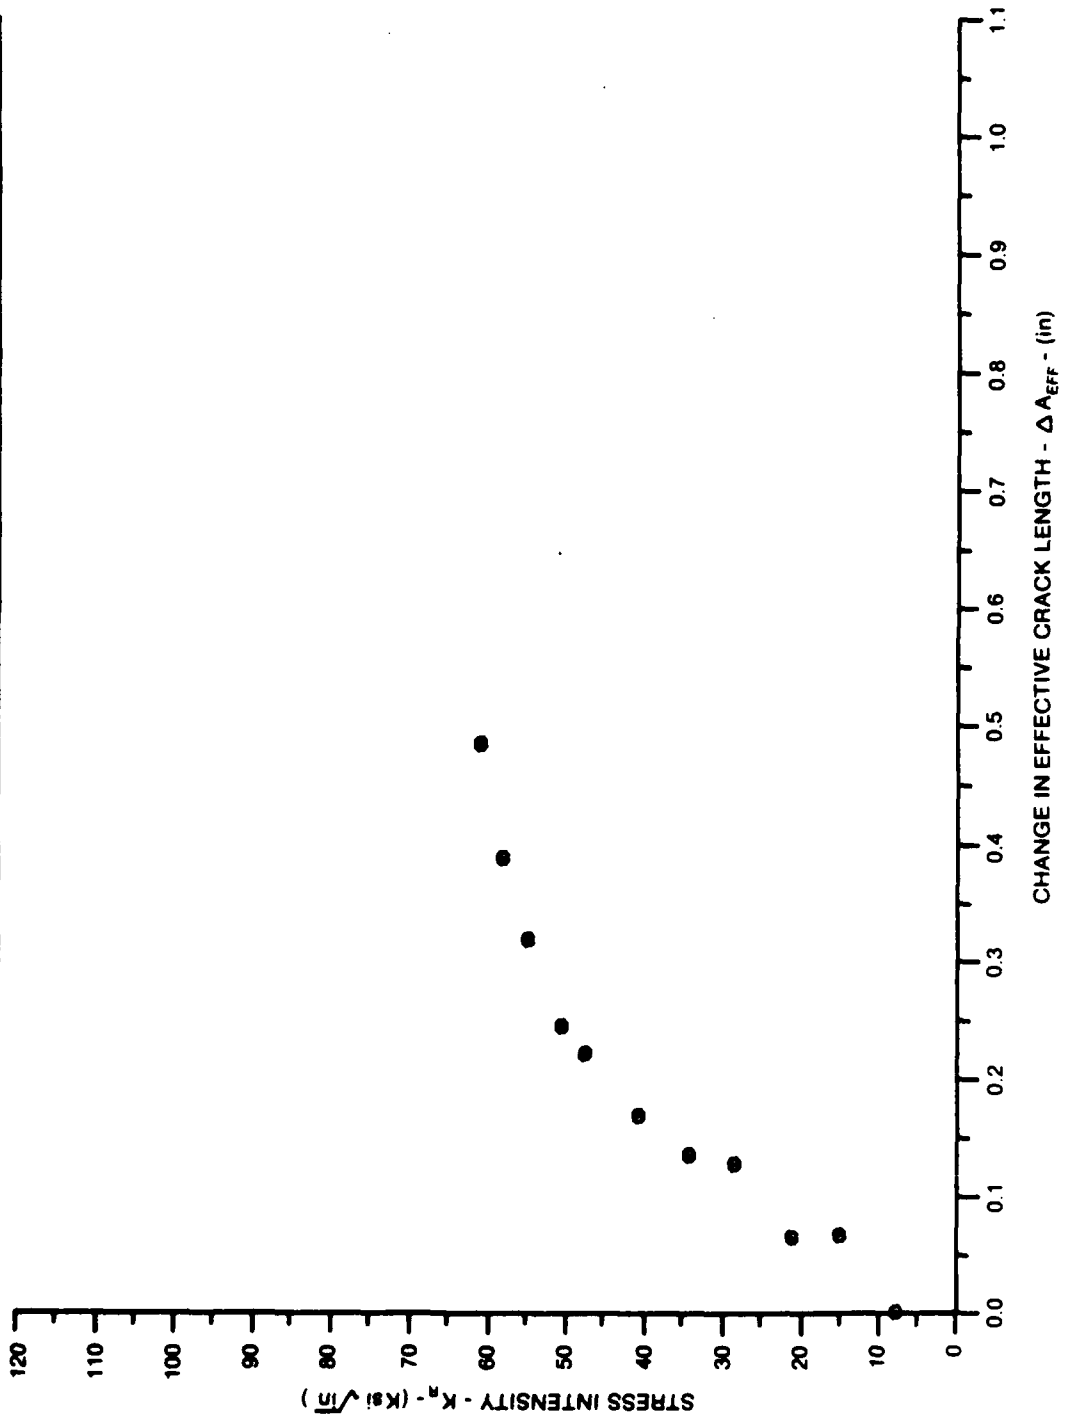


Figure 7.5.2.34

ALUM. ALLOY
2024

SPECIMEN THK: .126"
 SPECIMEN WIDTH: 6.010"
 K_C (Ksi√in): 56.8
 REFERENCE: GD005

CONDITION/HT: T81
 FORM: .13" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L

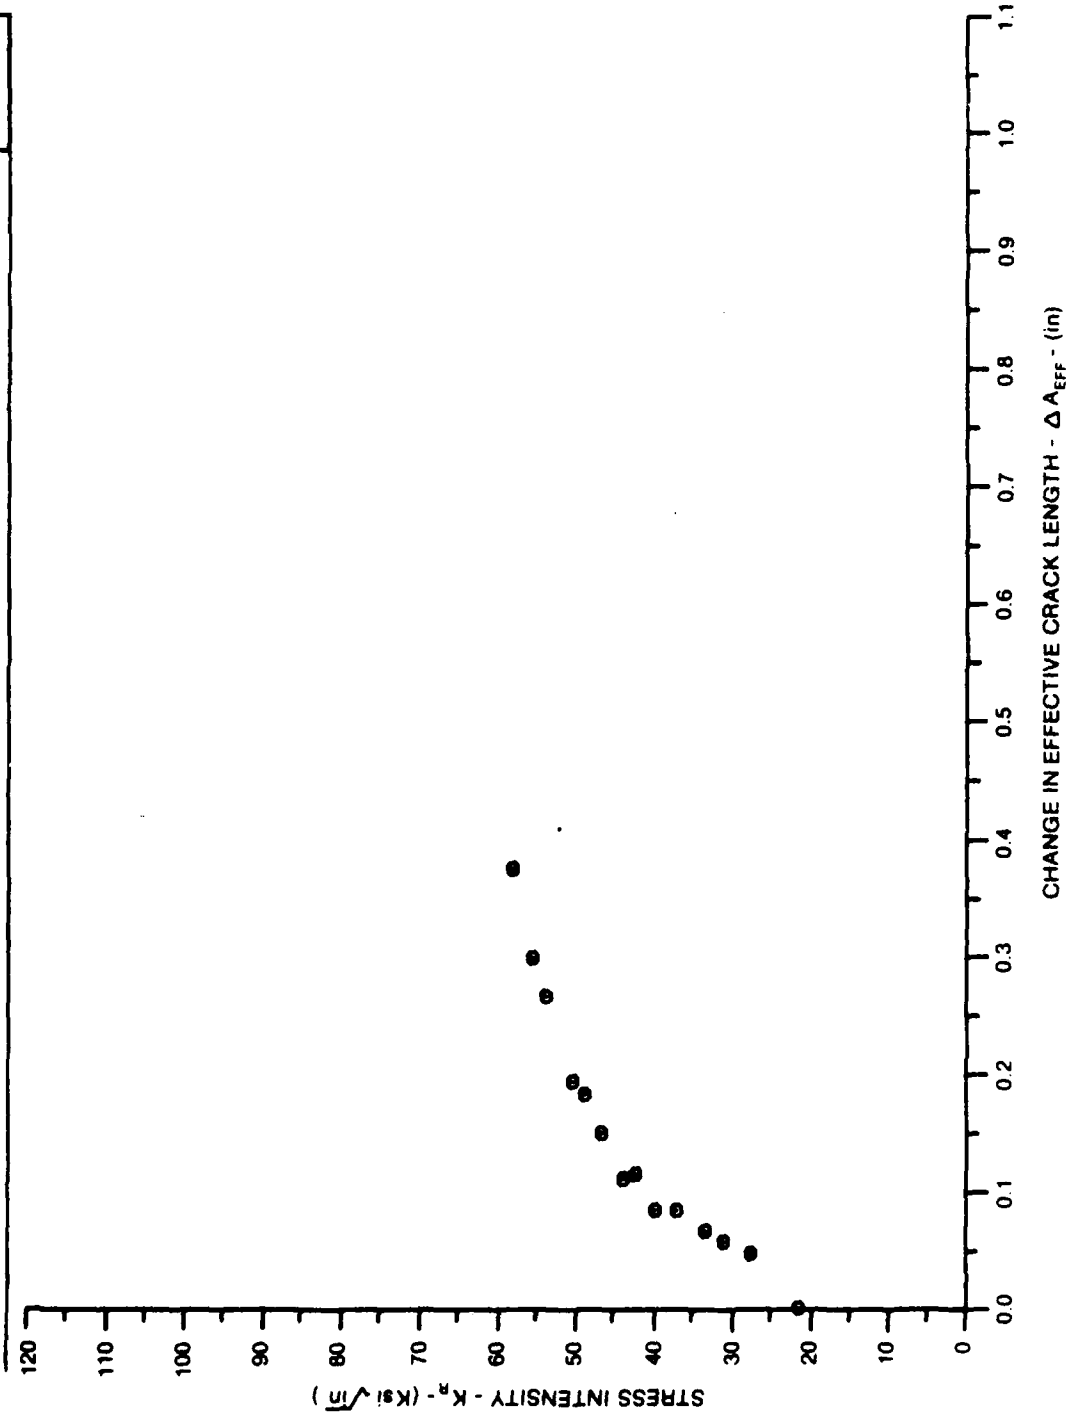


Figure 7.5.2.35

TABLE 7.5.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T3					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		R=+0.05	R=+0.40	R=+0.60	
DELTA K A:	2.63	.11			
DELTA K B:	4.24		.32		
MIN C:	3.58			.25	
D:					
	3.00	.110			
	3.50	.120			
	4.00	.146		.373	
	5.00	.258	.946	1.22	
	6.00	.497	1.92		
	7.00	.976			
	8.00	1.89			
	9.00	3.57			
DELTA K A:	9.56	5.03			
MAX B:	6.24		2.19		
C:	5.02			1.24	
D:					
ROOT MEAN SQUARE		33.02	2.95	8.28	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25	3	1	1	
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: T3
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 30.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 47.2 KSI
 ULT. STRENGTH: 68.2 KSI
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 13.985- 14.030"
 REFERENCES: EFM01

ALUM. ALLOY
2024

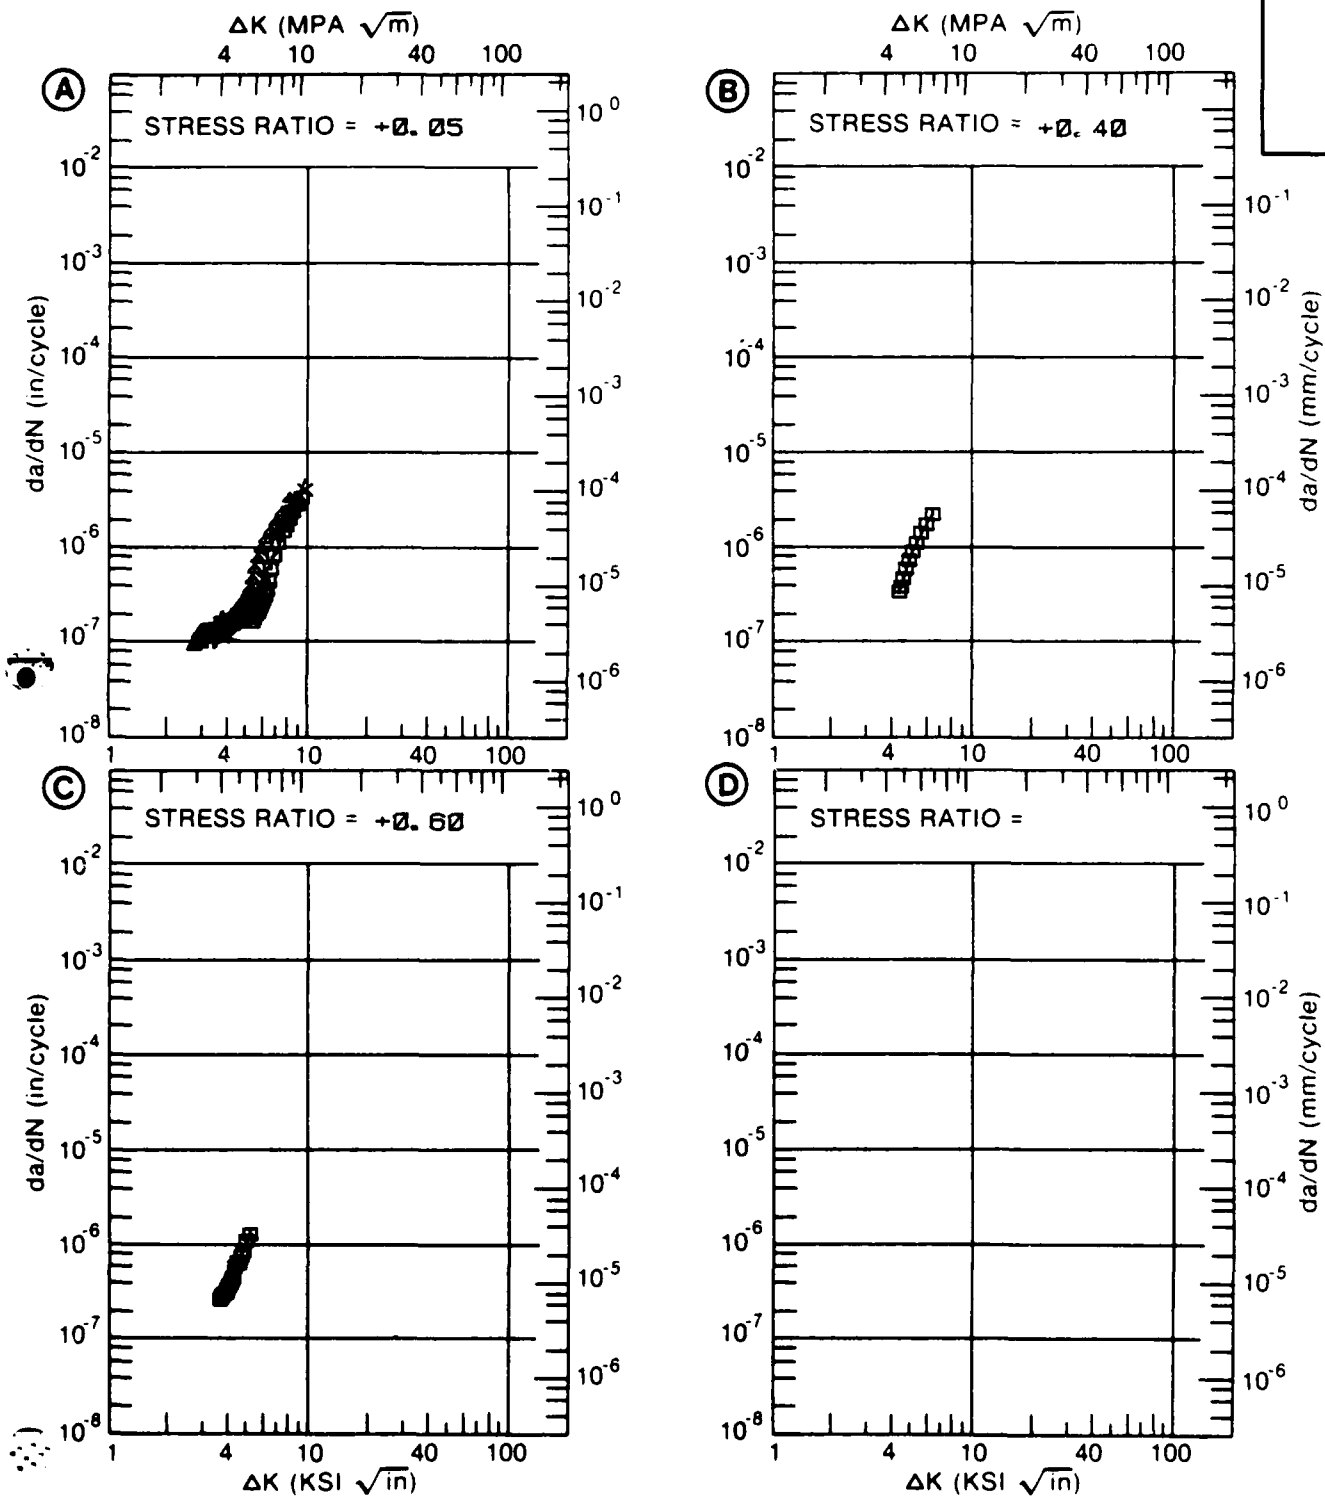


Figure 7.5.3.1

TABLE 7.5.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T3					
ENVIRONMENT: + 140F, AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.40	R=+0.70		
DELTA K MIN	A: 3.16	.131			
	B: 3.05		.151		
	C:				
	D:				
	3.50	.181	.343		
	4.00	.301	.679		
	5.00	.794	1.77		
	6.00	1.80	3.45		
	7.00	3.40	5.85		
	8.00	5.48	9.27		
	9.00	7.65	14.2		
	10.00	9.43	21.3		
DELTA K MAX	A: 11.11	10.5			
	B: 11.74		42.7		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		15.62	7.32		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1		

CONDITION/HT: T3
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 5.00- 10.00 HZ
 ENVIRONMENT: + 140° F. AIR

YIELD STRENGTH: 47.2 KSI
 ULT. STRENGTH: 68.2 KSI
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 36.000"
 REFERENCES: EFM01

ALUM.
ALLOY

2024

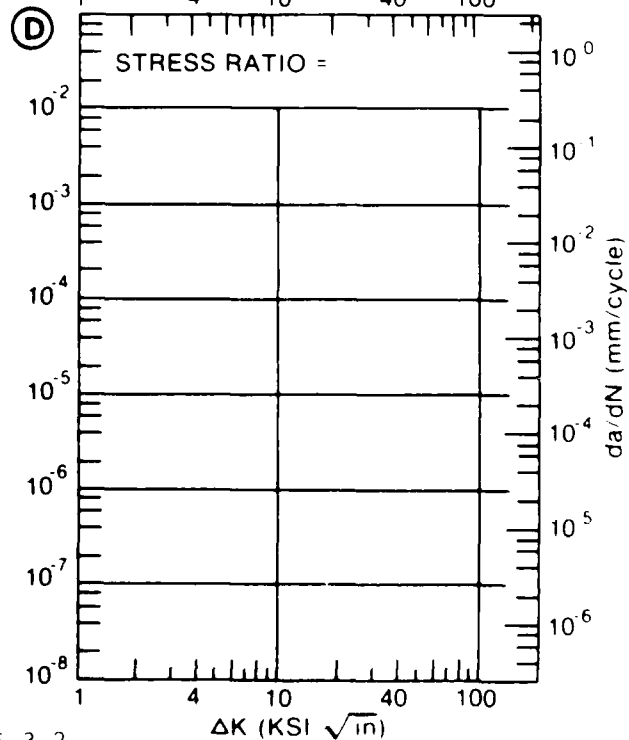
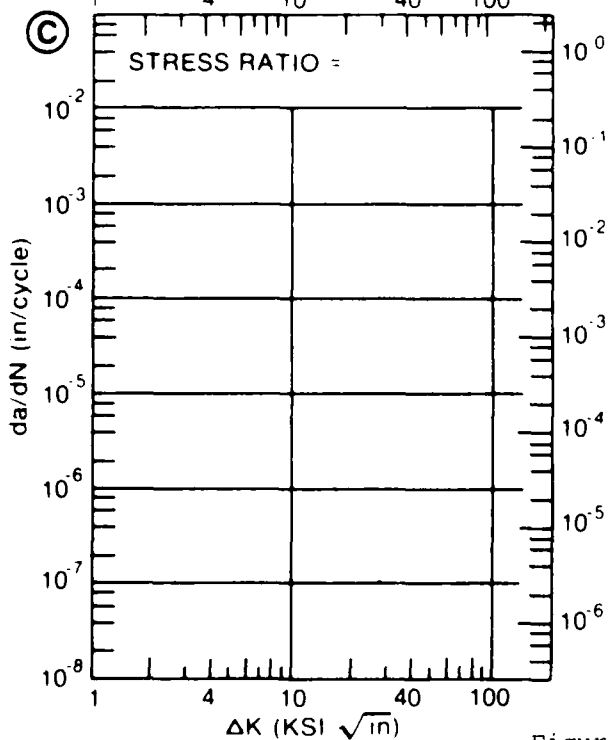
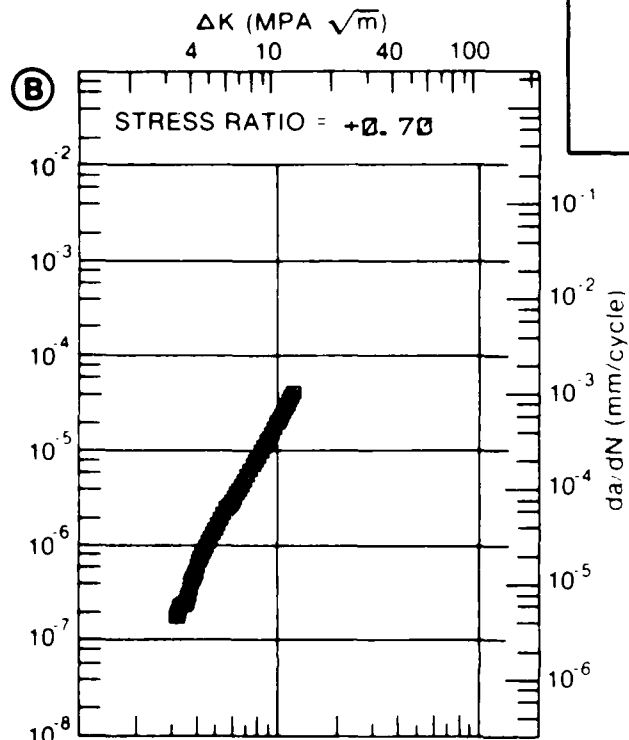
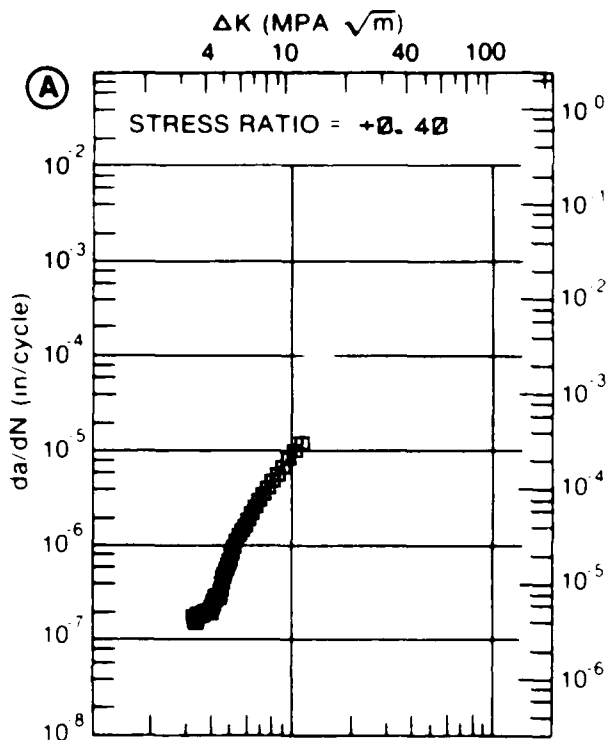


Figure 7.5.3.2

TABLE 7.5.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.3 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T3					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.33			
DELTA K MIN	A: 12.30	16.4			
	B:				
	C:				
	D:				
	13.00	19.3			
	16.00	48.3			
	20.00	188.			
	25.00	887.			
	30.00	3138.			
DELTA K MAX	A: 31.48	4312.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		22.14			
PERCENT ERROR					
LIFE PREDICTION	0.0-0.5				
RATIO	0.5-0.8	2			
SUMMARY (NP/NA)	0.8-1.25	4			
	1.25-2.0				
	>2.0				

CONDITION/HT: T3
 FORM: 0.04" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 3.33 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 45.0 KSI
 ULT. STRENGTH: 69.0 KSI
 SPECIMEN THK: 0.039"
 SPECIMEN WIDTH: 16.000"
 REFERENCES: 87398

ALUM. ALLOY

2024

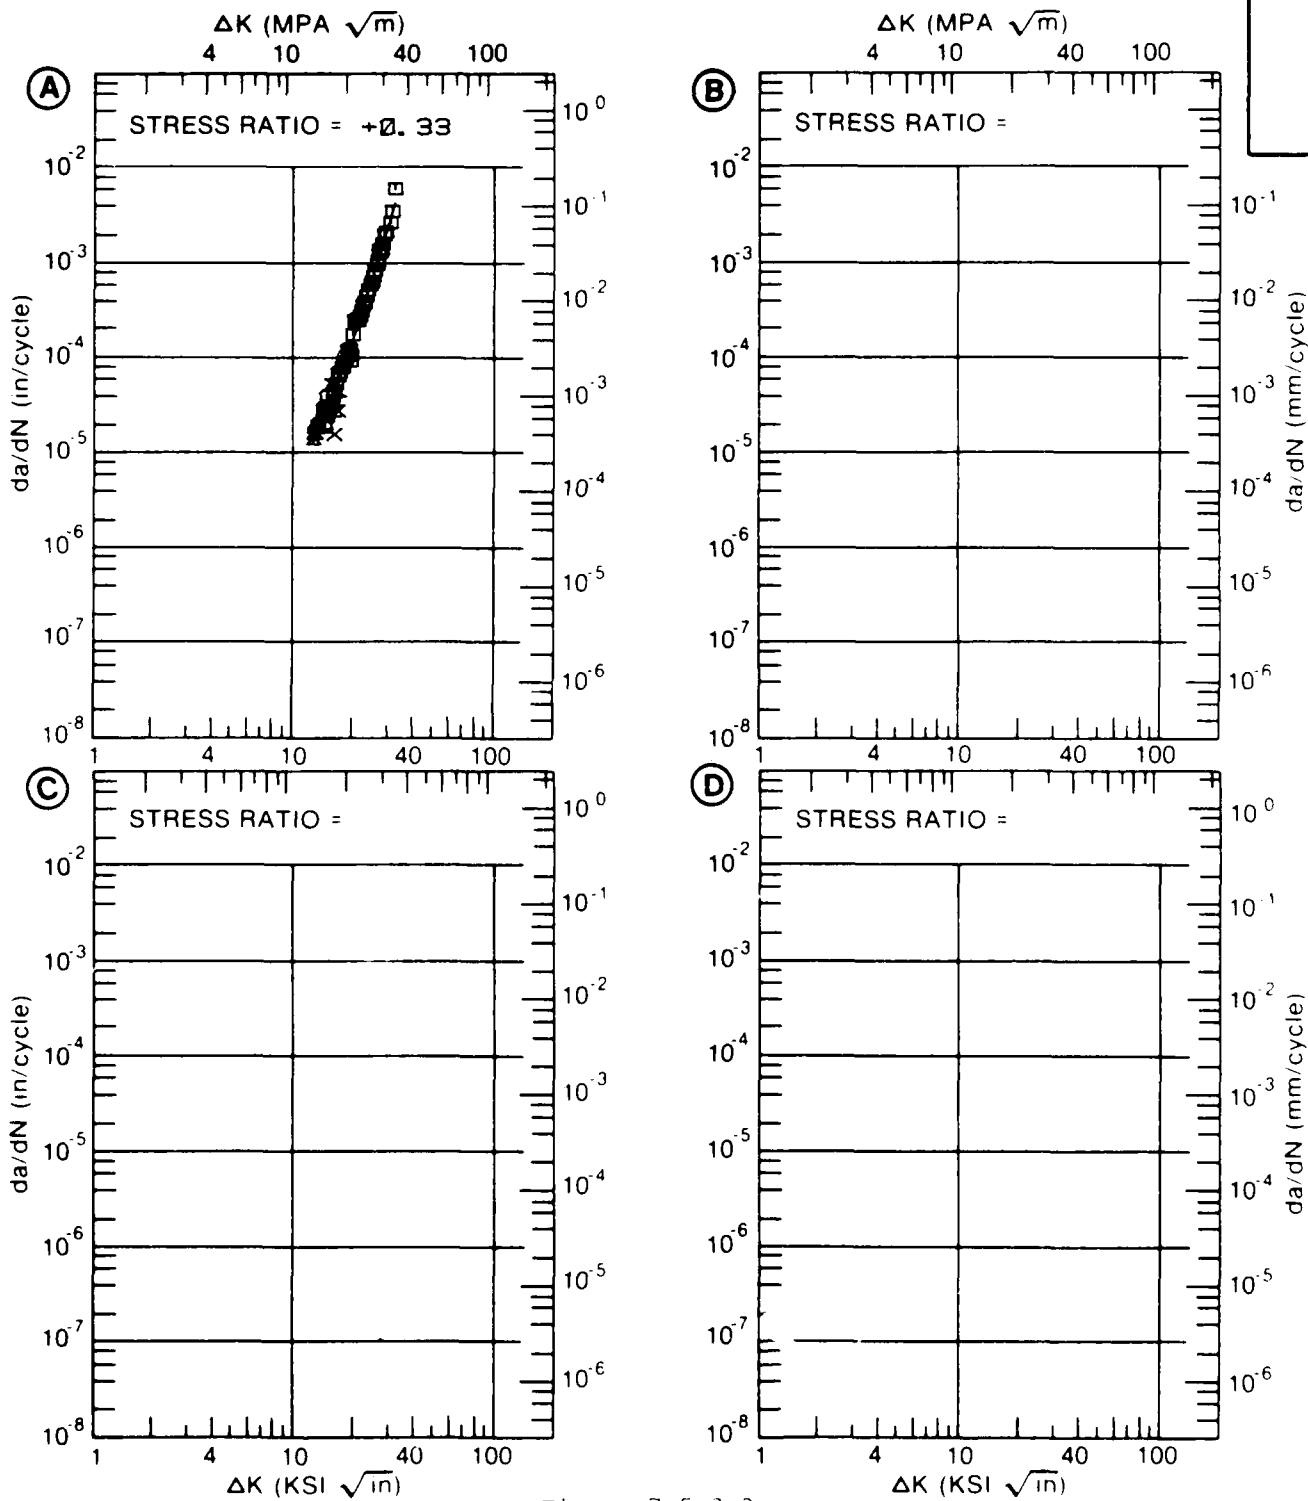


Figure 7.5.3.3

TABLE 7.5.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T3					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.20			
DELTA K	A: 4.73	.0896			
MIN	B:				
	C:				
	D:				
	5.00	.219			
	6.00	2.20			
	7.00	4.76			
	8.00	6.90			
	9.00	8.55			
	10.00	9.72			
	13.00	12.1			
	16.00	15.6			
	20.00	27.9			
	25.00	85.0			
DELTA K	A: 27.13	153.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		17.00			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	2			
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T3
 FORM: 0.09" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R.T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 4.010"
 REFERENCES: FR001

ALUM.
 ALLOY

2024

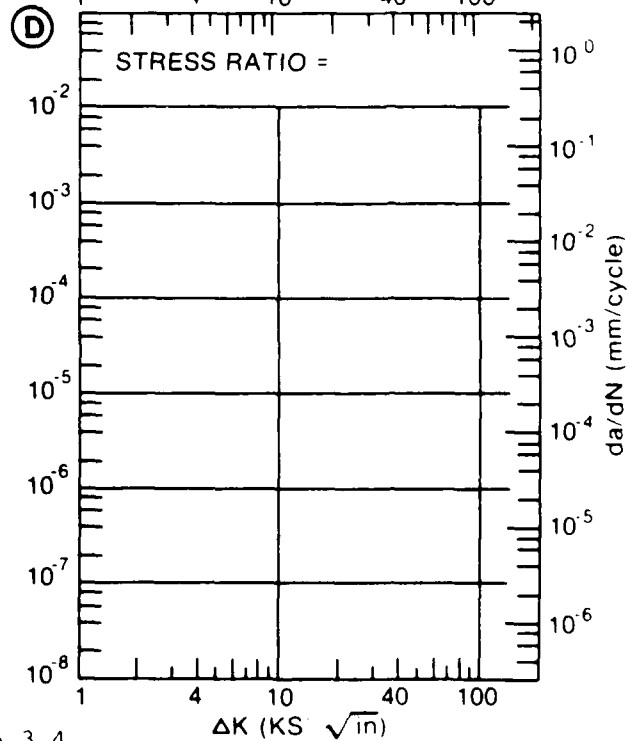
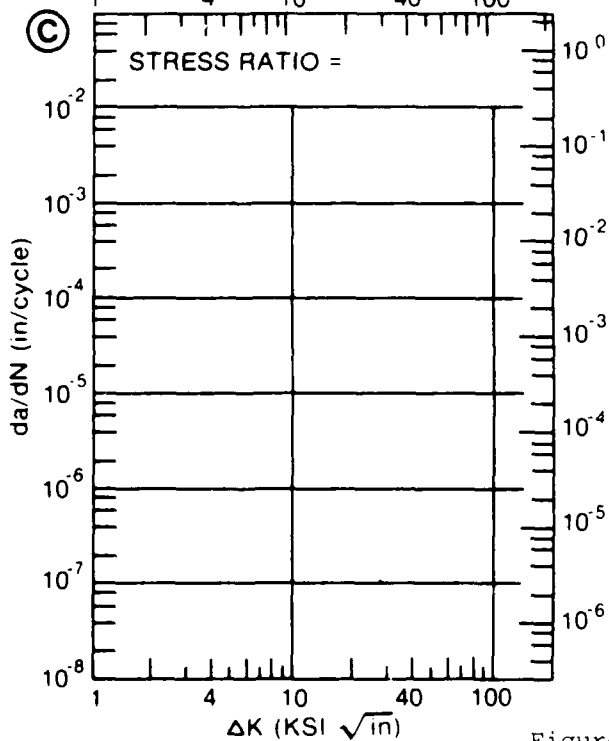
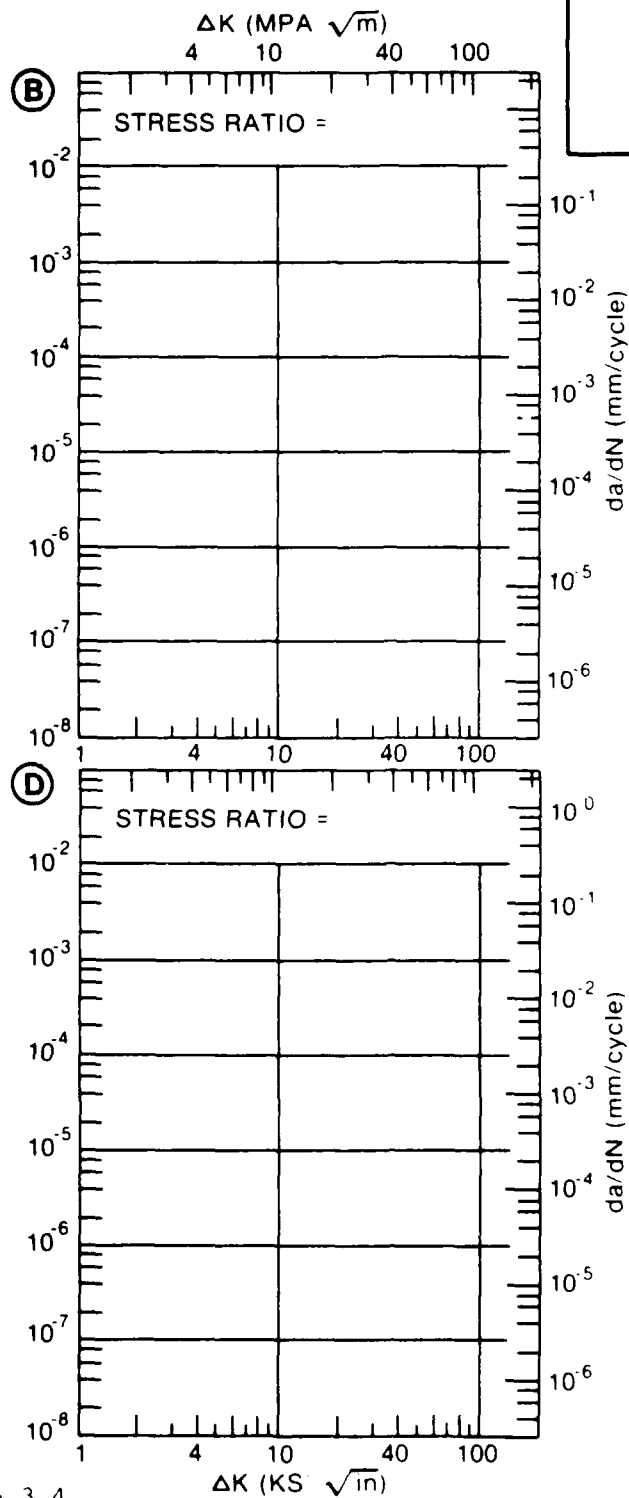
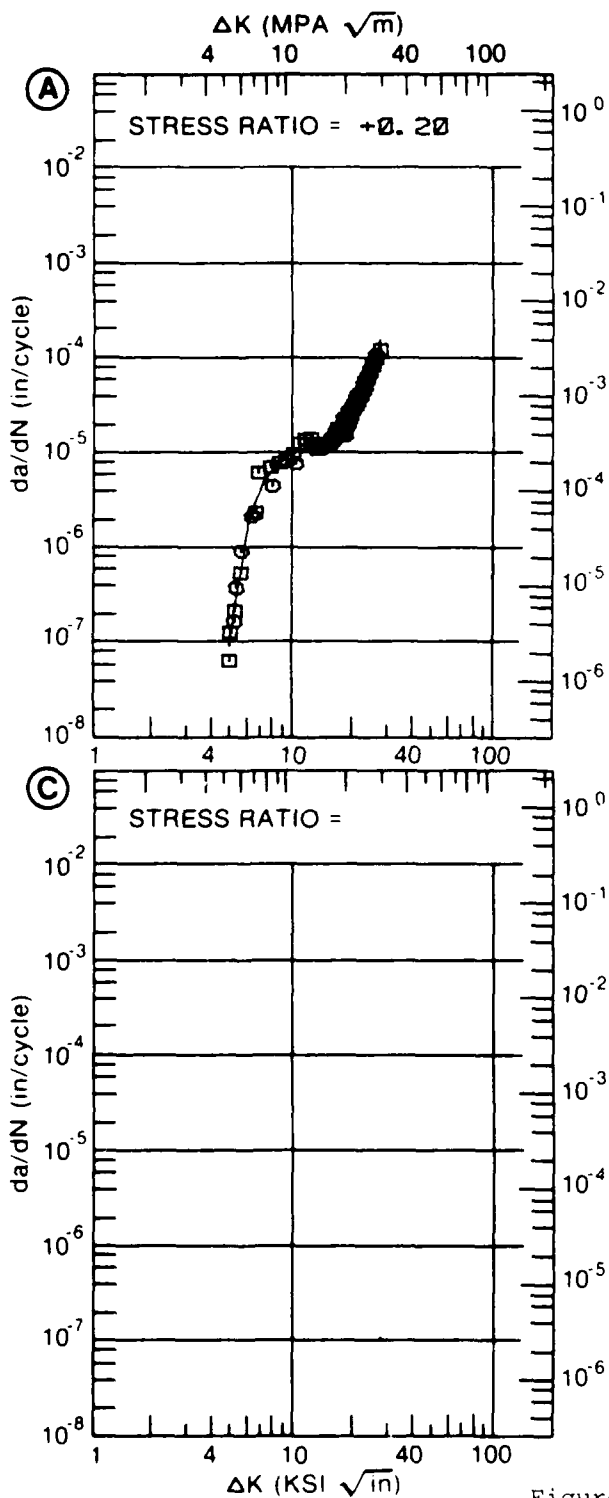


Figure 7.5.3.4

TABLE 7.5.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.5 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T3
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	R=+0.00			
A: 16.84	15.3			
DELTA K B:				
MIN C:				
D:				
20.00	28.6			
25.00	76.3			
30.00	184.			
35.00	390.			
A: 35.36	410.			
DELTA K B:				
MAX C:				
D:				

ROOT MEAN SQUARE 19.64
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	1
RATIO	0.8-1.25	7
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: T3
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 13.30 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 68.2 KSI
 SPECIMEN THK: 0.125- 0.126"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 86213

ALUM. ALLOY
2024

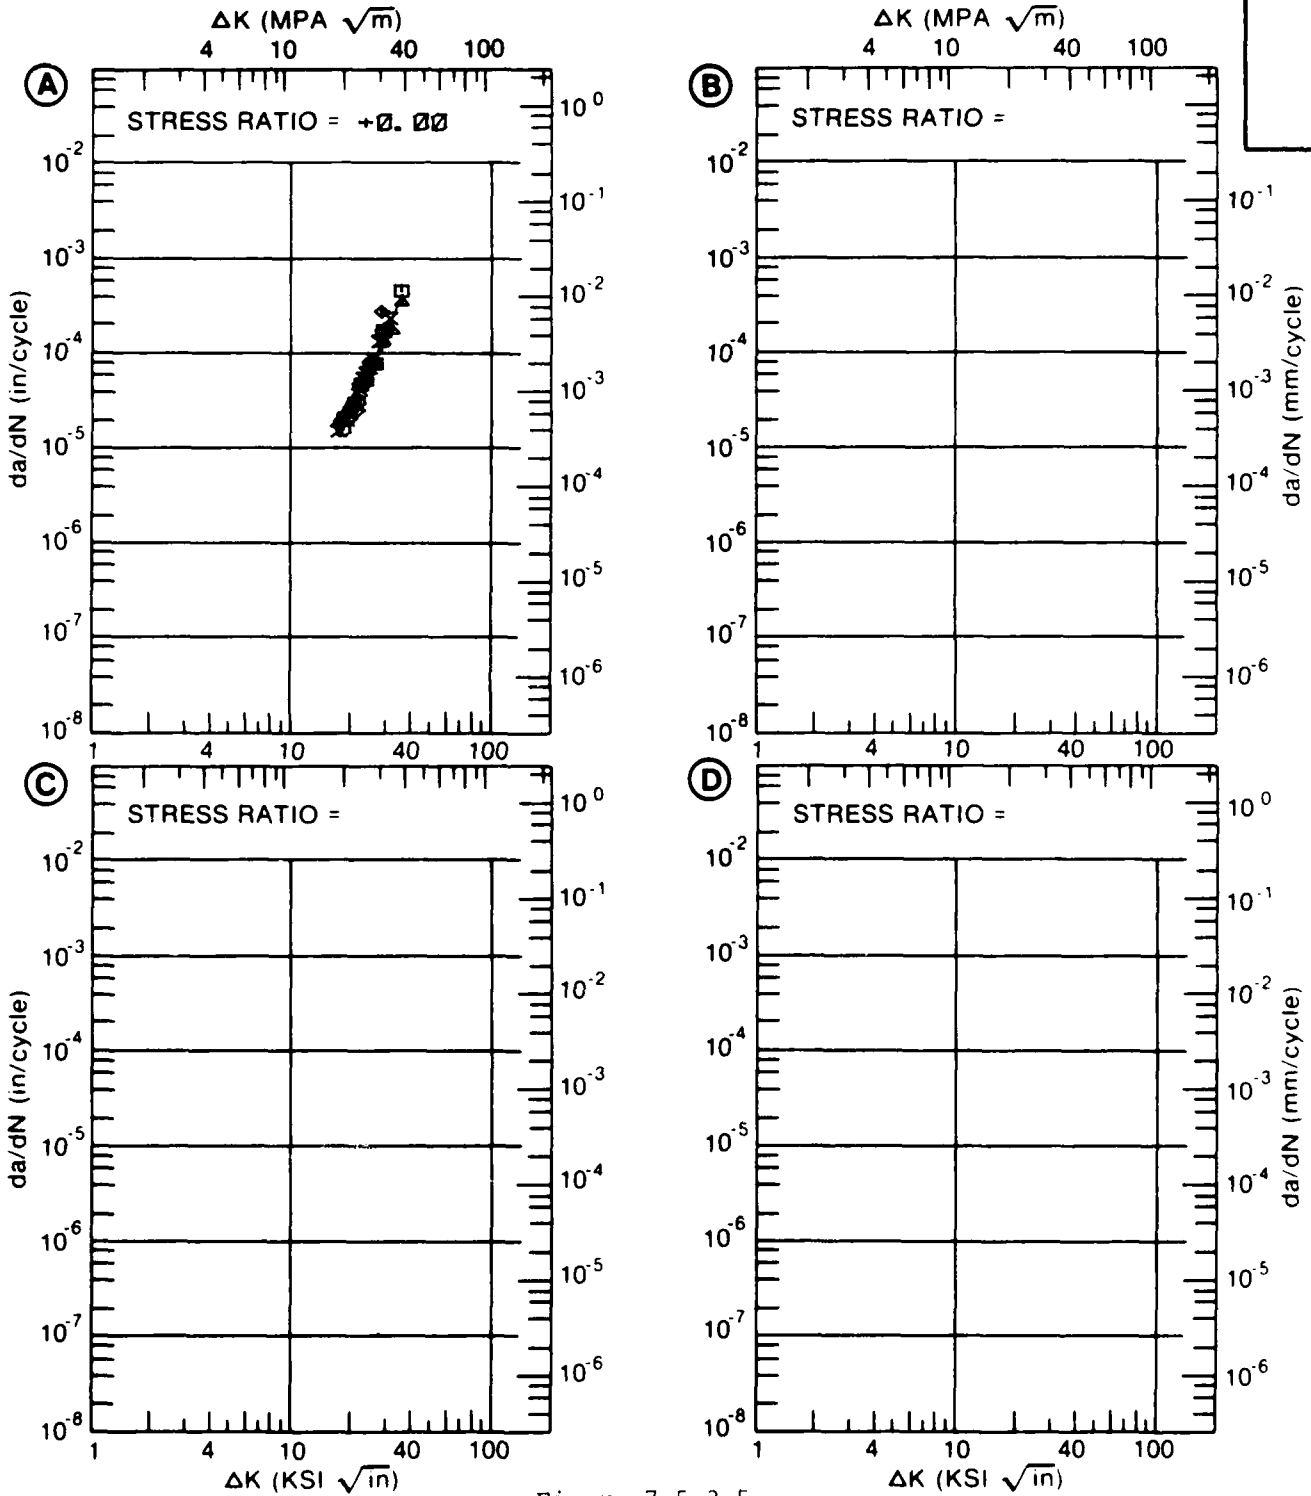


Figure 7.5.3.5

TABLE 7.5.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T3					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. 90% R. H.			
DELTA K	A: 13.10	10.6			
MIN	B:				
	C:				
	D:				
	16.00	18.4			
	20.00	35.3			
	25.00	71.3			
	30.00	133.			
	35.00	234.			
DELTA K	A: 37.88	318.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		21.03			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T3
 FORM: Ø. 13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +Ø. Ø5
 FREQUENCY: 2. ØØ HZ

YIELD STRENGTH: 49.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: Ø. 128"
 SPECIMEN WIDTH: 12. ØØØ"
 REFERENCES: Ø6212

ALUM. ALLOY
2Ø24

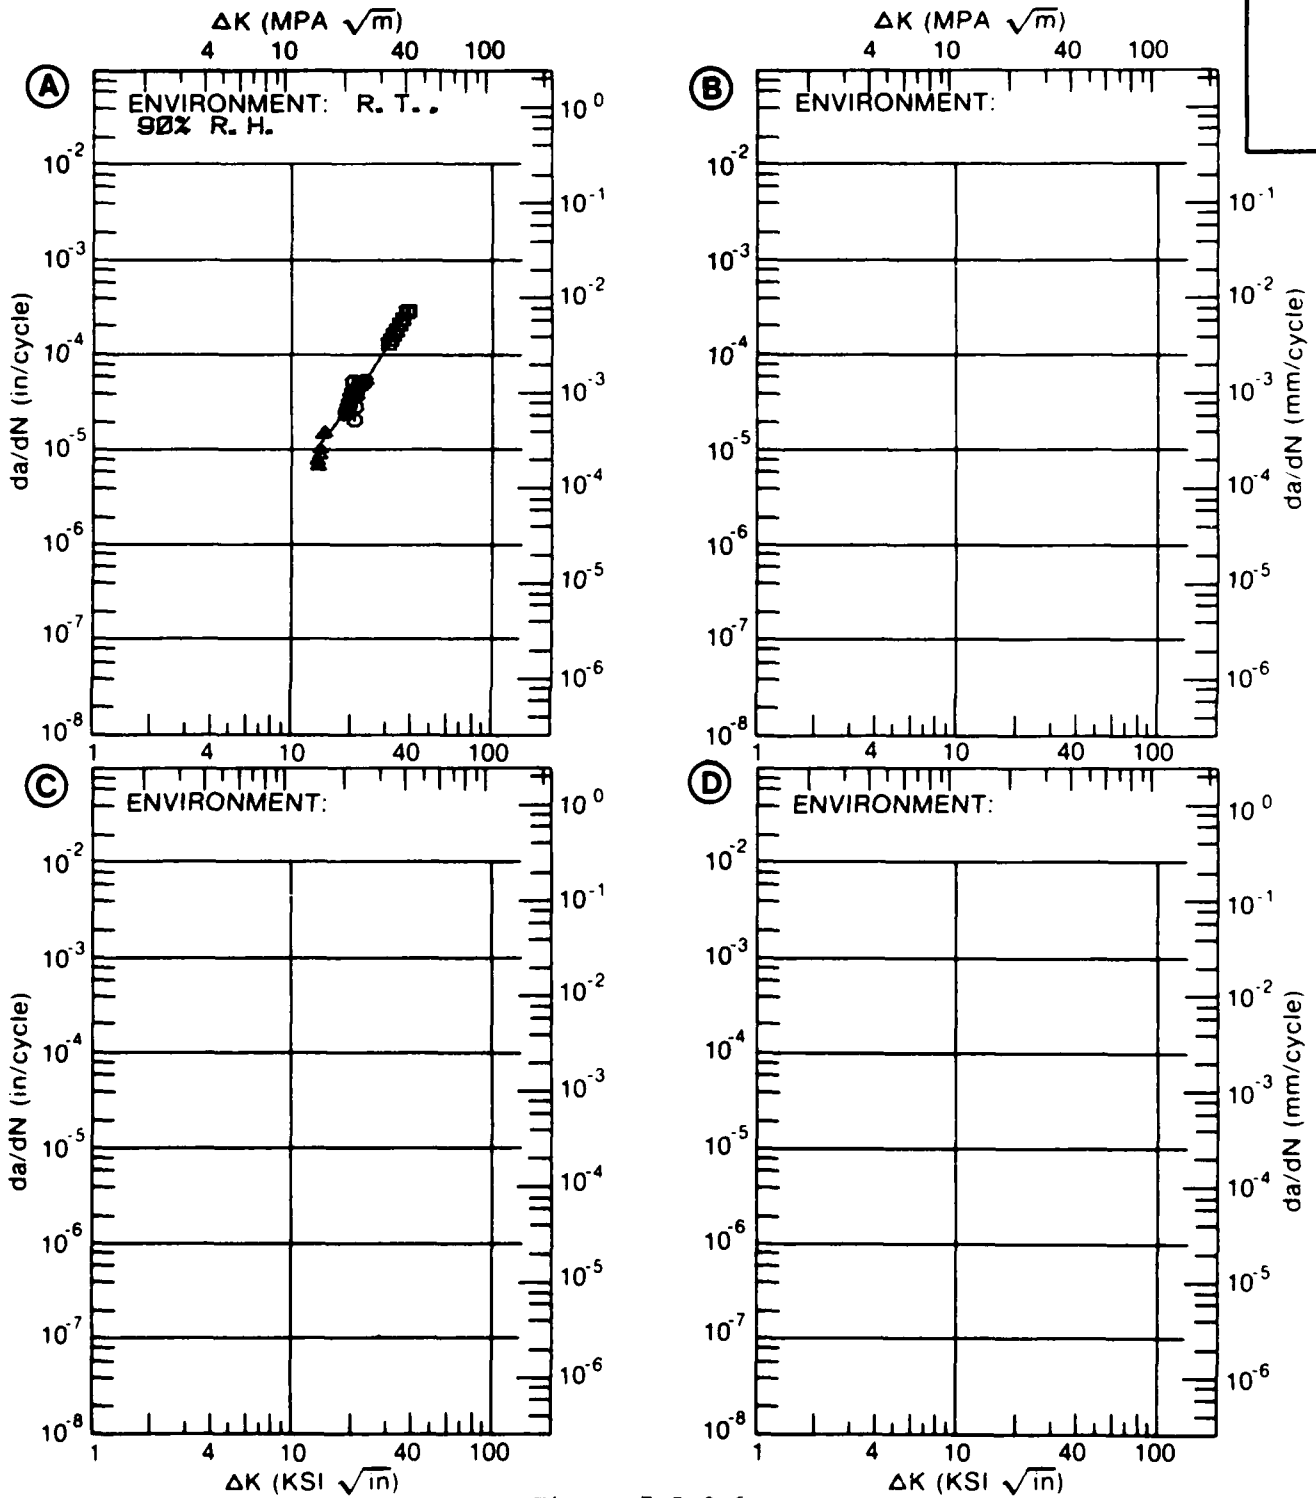


Figure 7.5.3.6

TABLE 7.5.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.7 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T3					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-1.00	R=-0.50	R=+0.05	
DELTA K MIN	A: 5.03	.119			
	B: 4.59		.129		
	C: 5.78			.238	
	D:				
	5.00		.144		
	6.00	.495	.755	.351	
	7.00	1.43	2.66	1.34	
	8.00	3.15	5.78	3.25	
	9.00	5.77	9.49	5.99	
	10.00	9.29	13.2	9.36	
	13.00	24.0	23.1	22.7	
	16.00	41.4	35.2	45.3	
	20.00	70.3	67.2		
DELTA K MAX	A: 24.85	264.			
	B: 24.91		175.		
	C: 19.55			102.	
	D:				
ROOT MEAN SQUARE		24.20	19.99	12.63	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25				
	1.25-2.0				
	>2.0				

CONDITION/HT: T3
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R.T., LAB AIR

YIELD STRENGTH: 50.9 KSI
 ULT. STRENGTH: 68.5 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: UD006

ALUM.
ALLOY

2024

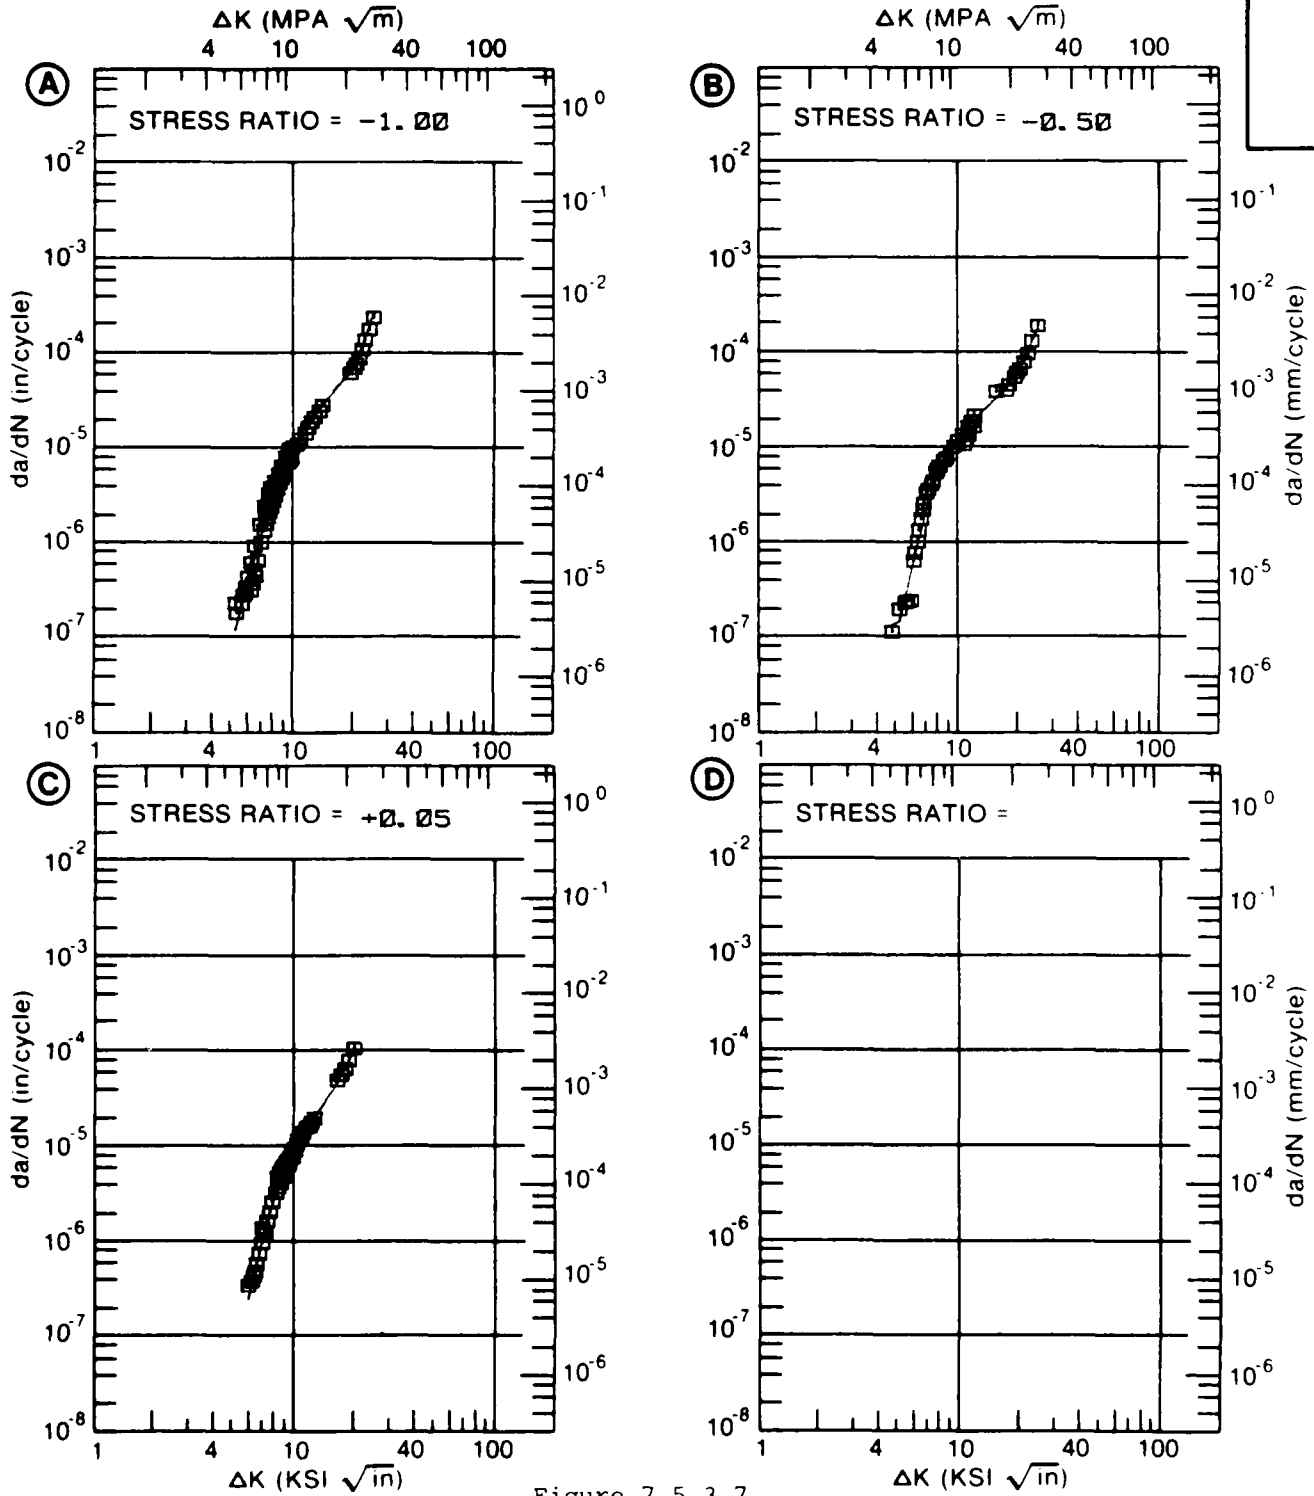


Figure 7.5.3.7

TABLE 7.5.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.8 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024		
CONDITION: T351				
ENVIRONMENT: - 65F, AIR				
DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	R=+0.00	R=+0.80		
DELTA K MIN	A: 9.84	.354	B: 6.02	.766
	C: 7.00		D: 1.96	
	8.00		4.70	
	9.00		10.2	
	10.00	.360	20.4	
	13.00	1.06	102.	
	16.00	4.50	303.	
	20.00	19.7		
	25.00	69.4		
DELTA K MAX	A: 29.42	208.	B: 17.13	414.
	C:		D:	
ROOT MEAN SQUARE	26.82		10.41	
PERCENT ERROR				
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5		0.5-0.8	1
	0.8-1.25		1.25-2.0	1
	>2.0			

CONDITION/HT: T351
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY:
 ENVIRONMENT: - 65° F. AIR

YIELD STRENGTH: 56.9 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.184- 0.188"
 SPECIMEN WIDTH: 11.997- 12.000"
 REFERENCES: DA001

ALUM.
 ALLOY

2024

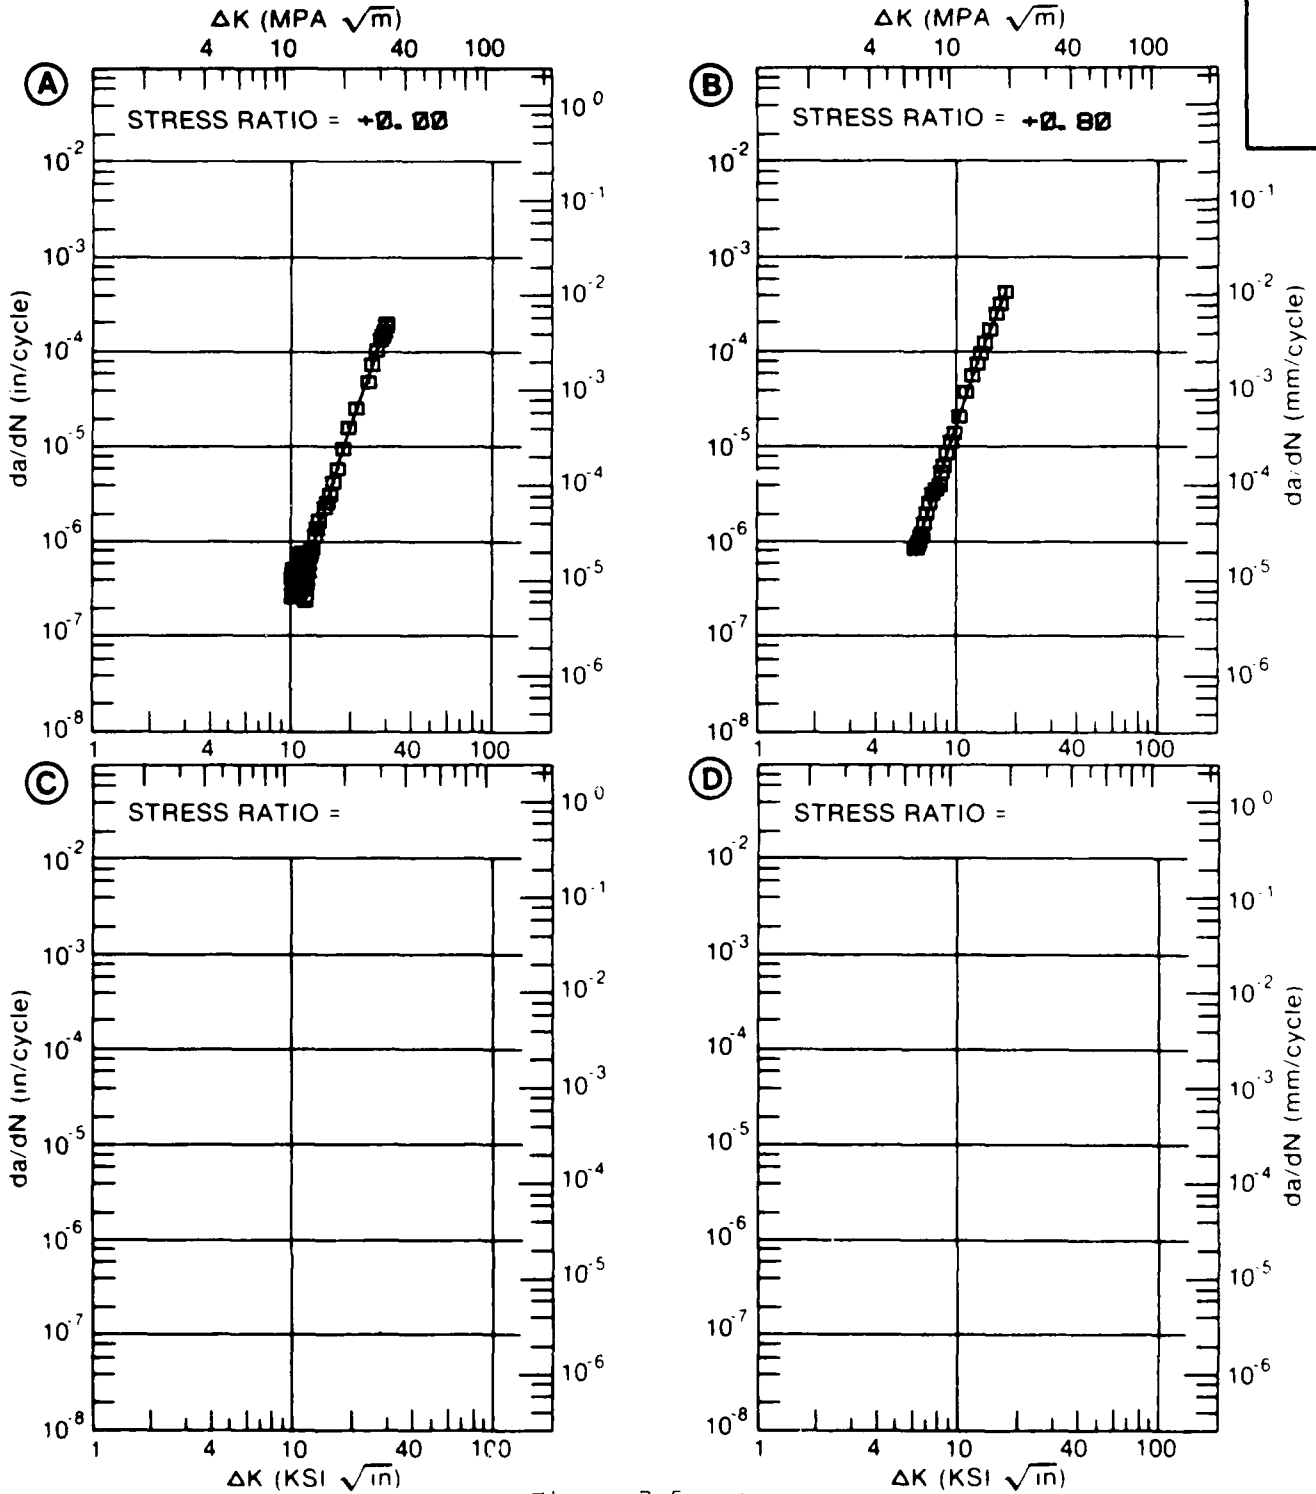


Figure 7.5.

TABLE 7.5.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.9 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.40	R=+0.80	
DELTA K	A: 9.51	5.14			
MIN	B: 15.81		60.3		
	C: 7.98			13.8	
	D:				
	8.00			14.0	
	9.00			23.4	
	10.00	6.16		39.2	
	13.00	13.6		167.	
	16.00	23.5	63.5	553.	
	20.00	44.0	163.		
	25.00		419.		
	30.00		935.		
DELTA K	A: 24.94	95.5			
MAX	B: 33.80		1628.		
	C: 17.04			790.	
	D:				
ROOT MEAN SQUARE		3.46	5.76	15.15	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 3.00- 8.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 56.9 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.181- 0.186"
 SPECIMEN WIDTH: 11.998- 12.009"
 REFERENCES: DA001

ALUM. ALLOY
2024

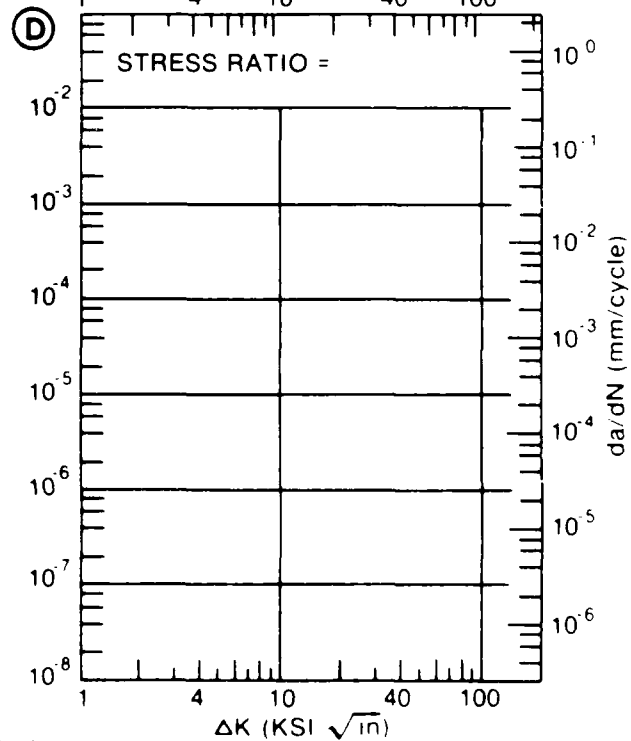
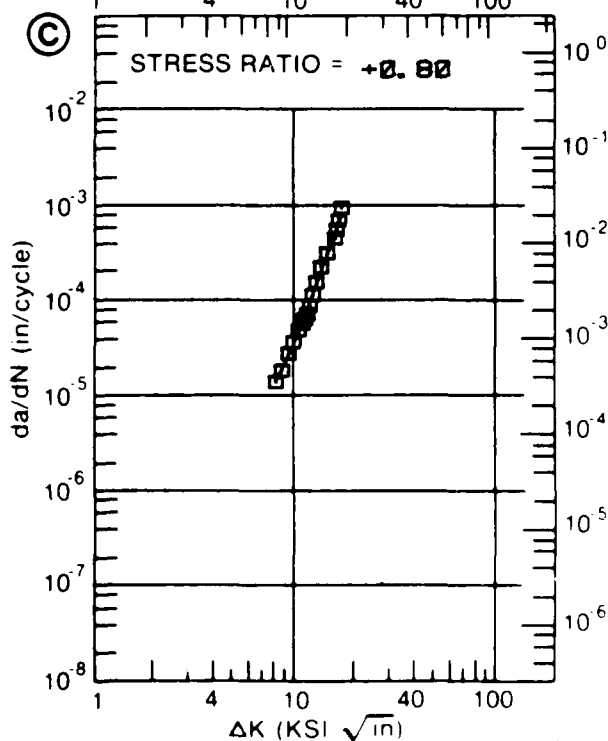
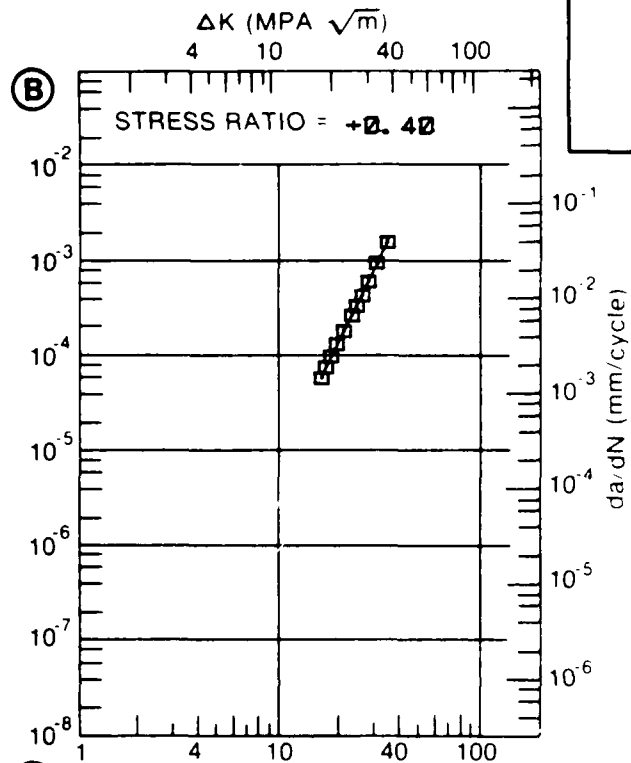
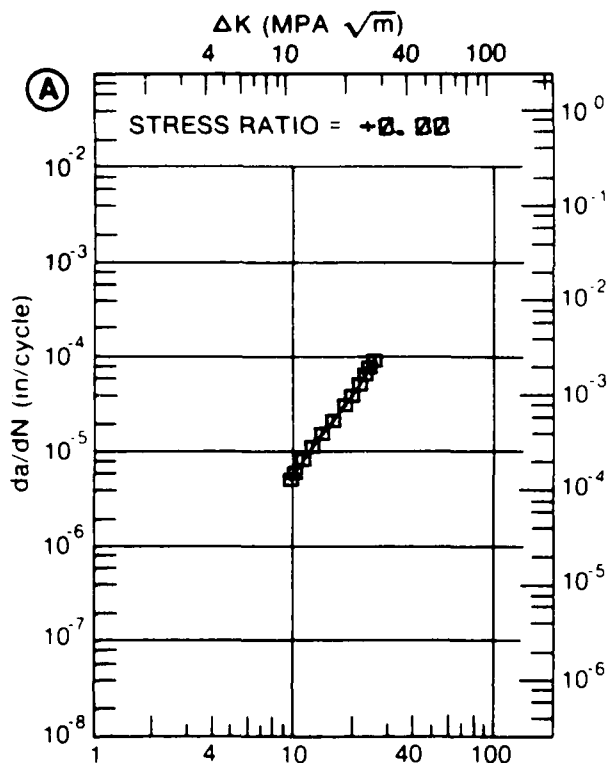


Figure 7.5.3.2

TABLE 7.5.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.10 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.70		
DELTA K MIN	A: 7.32	1.35			
	B: 4.72		.464		
	C:				
	D:				
	5.00		.636		
	6.00		1.50		
	7.00		2.72		
	8.00	1.80	4.25		
	9.00	2.75	6.13		
	10.00	4.09	8.42		
	13.00	9.26	19.4		
DELTA K MAX	A: 15.05	11.4			
	B: 14.38		28.1		
	C:				
	D:				
ROOT MEAN SQUARE		18.10	14.22		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25				
	1.25-2.0				
	>2.0				

CONDITION/HT: T351
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 9.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.163"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: B7002

ALUM. ALLOY
2024

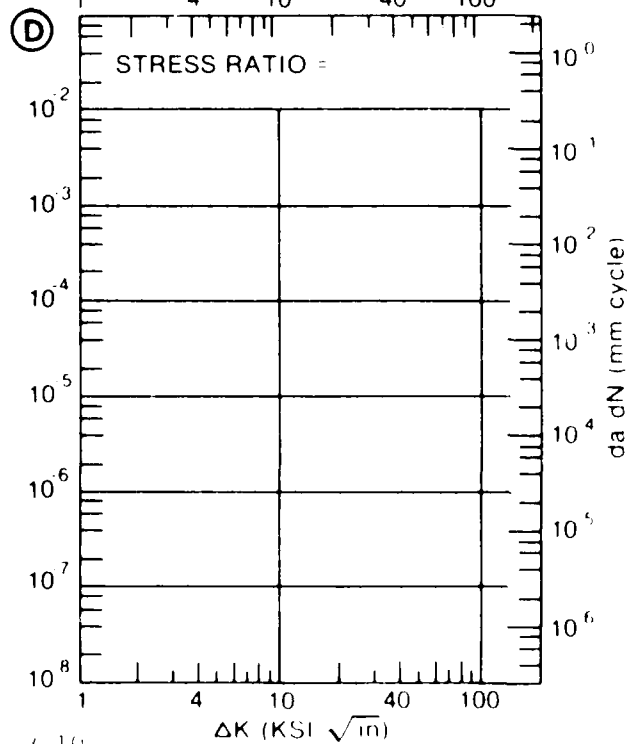
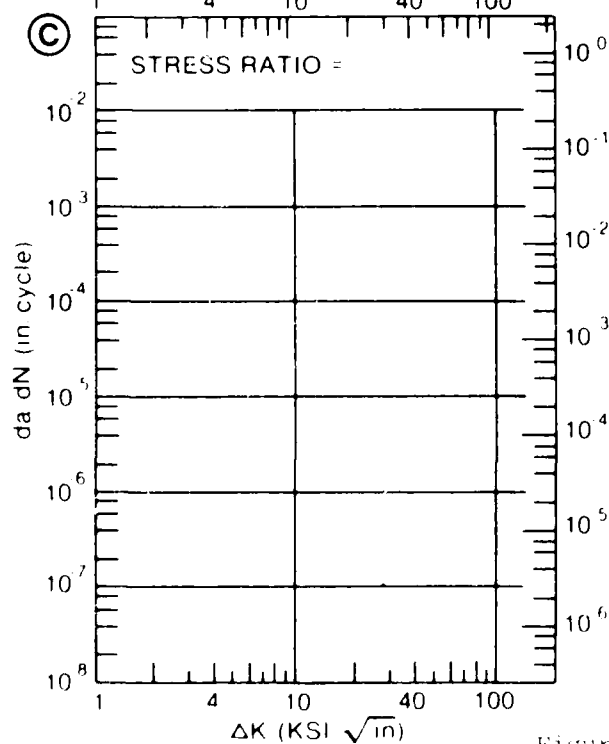
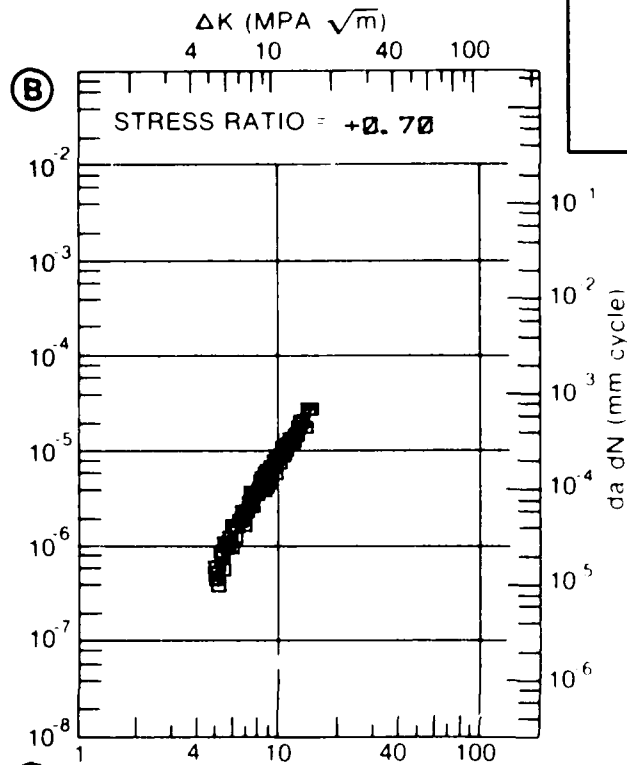
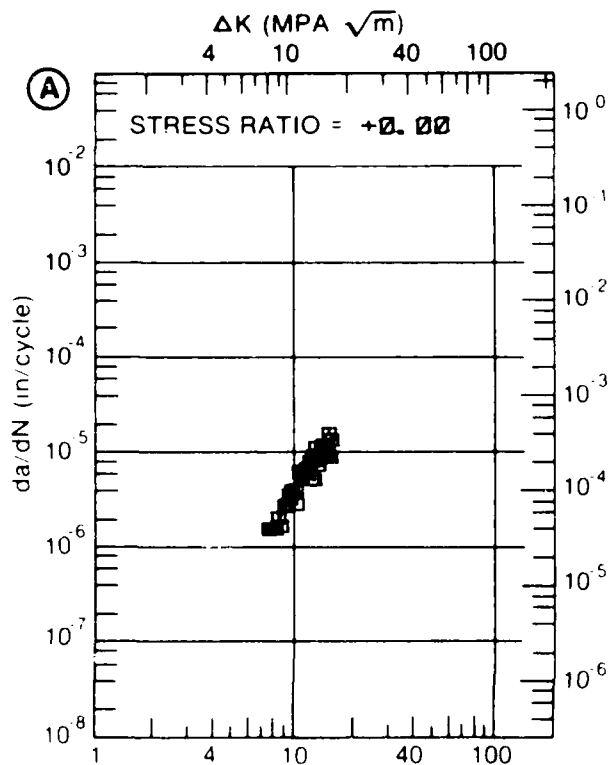


Figure 7.5.3.10

TABLE 7.5.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.11 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.33		
DELTA K	A: 8.77	2.31			
MIN	B: 11.68		19.2		
	C:				
	D:				
	9.00	2.46			
	10.00	3.21			
	13.00		25.1		
	16.00		49.6		
	20.00		113.		
DELTA K	A: 11.81	7.19			
MAX	B: 24.00		211.		
	C:				
	D:				
ROOT MEAN SQUARE		9.30	6.30		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00- 10.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 56.9 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.182- 0.192"
 SPECIMEN WIDTH: 12.000"
 REFERENCES: DA001

ALUM.
ALLOY

2024

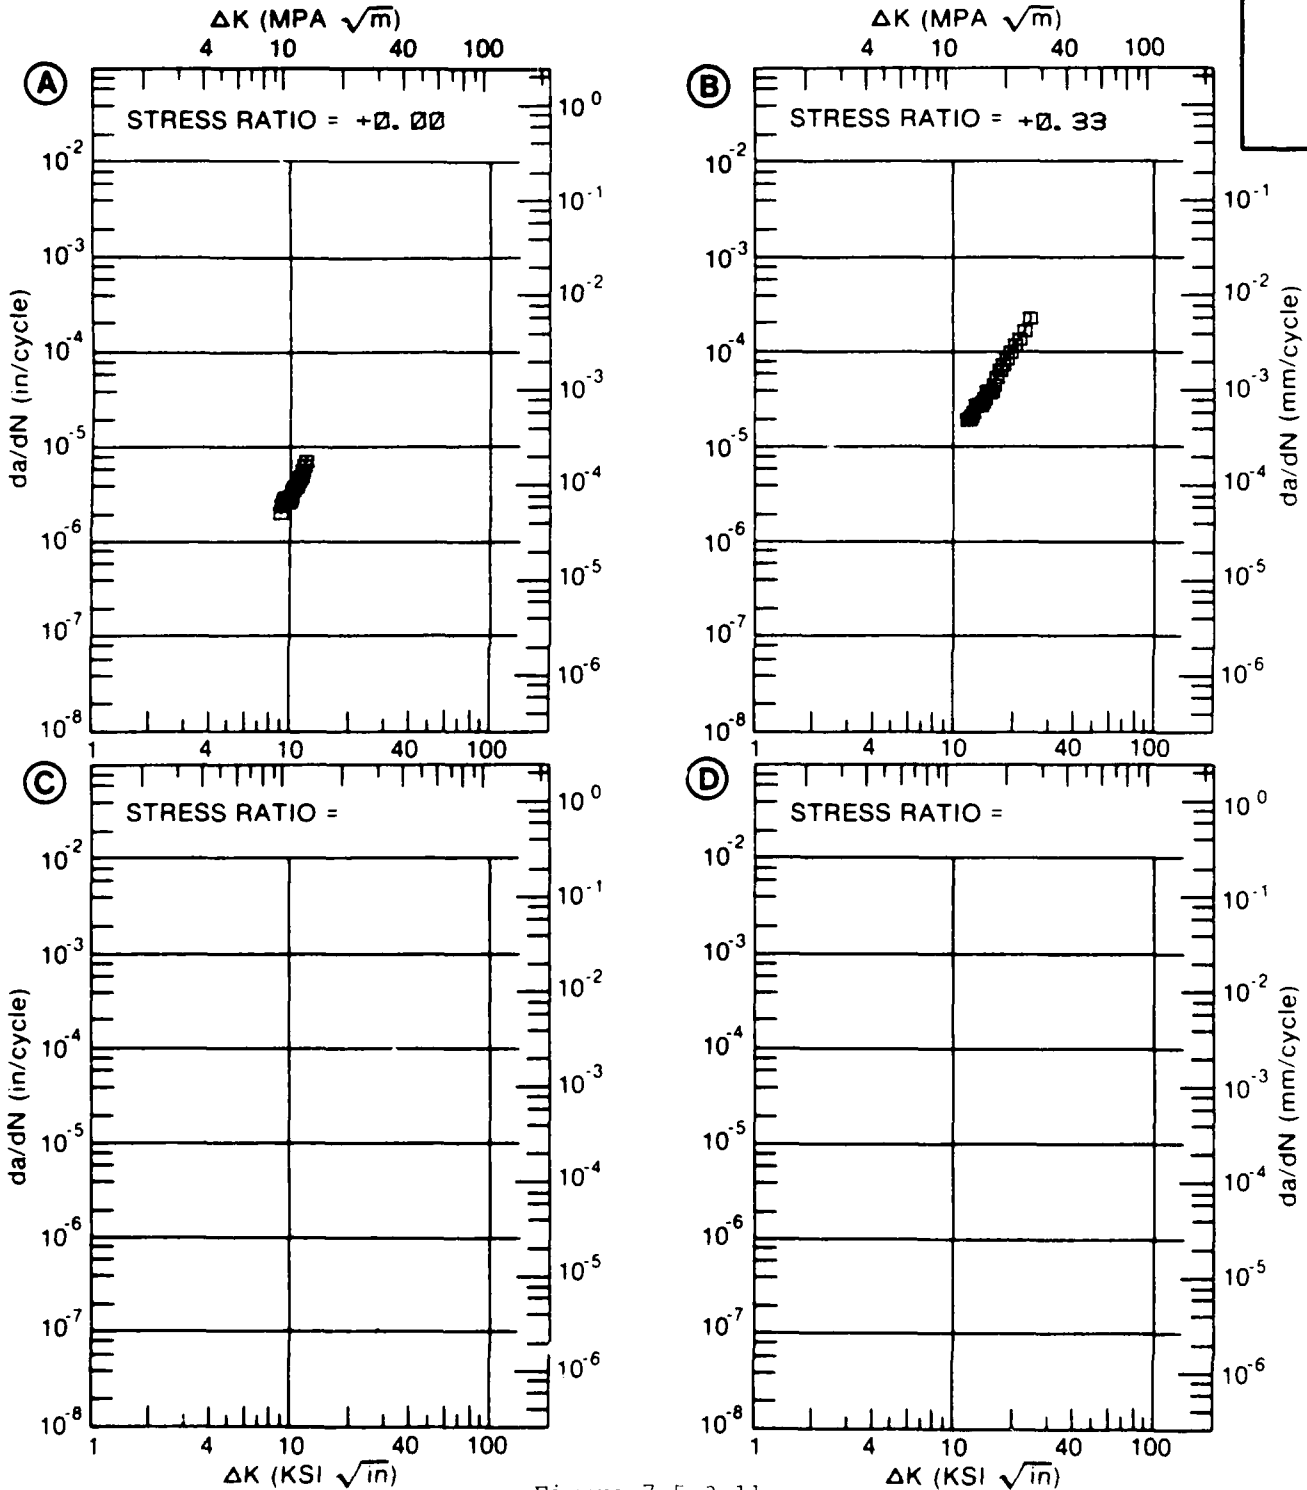


Figure 7.5.3.11

TABLE 7.5.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.12 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: R. T , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=-1.00	R=-0.50		
DELTA K MIN	A: 3.50	.159			
	B: 2.80		.0919		
	C:				
	D:				
	3.00		.0936		
	3.50	.159	.107		
	4.00	.161	.133		
	5.00	.270	.254		
	6.00	.620	.575		
	7.00	1.60	1.40		
	8.00	3.91	3.04		
	9.00	7.26	5.43		
	10.00	9.44	7.87		
	13.00	12.4	13.7		
	16.00	27.3	21.0		
	20.00	41.3	47.3		
	25.00		115.		
DELTA K MAX	A: 20.00	41.3			
	B: 27.15		140.		
	C:				
	D:				
ROOT MEAN SQUARE		10.20	15.32		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1		

CONDITION/HT: 351
 FORM: PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 3.00- 5.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 54.5 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.242"
 SPECIMEN WIDTH: 9.000"
 REFERENCES: DA001

ALUM.
ALLOY

2024

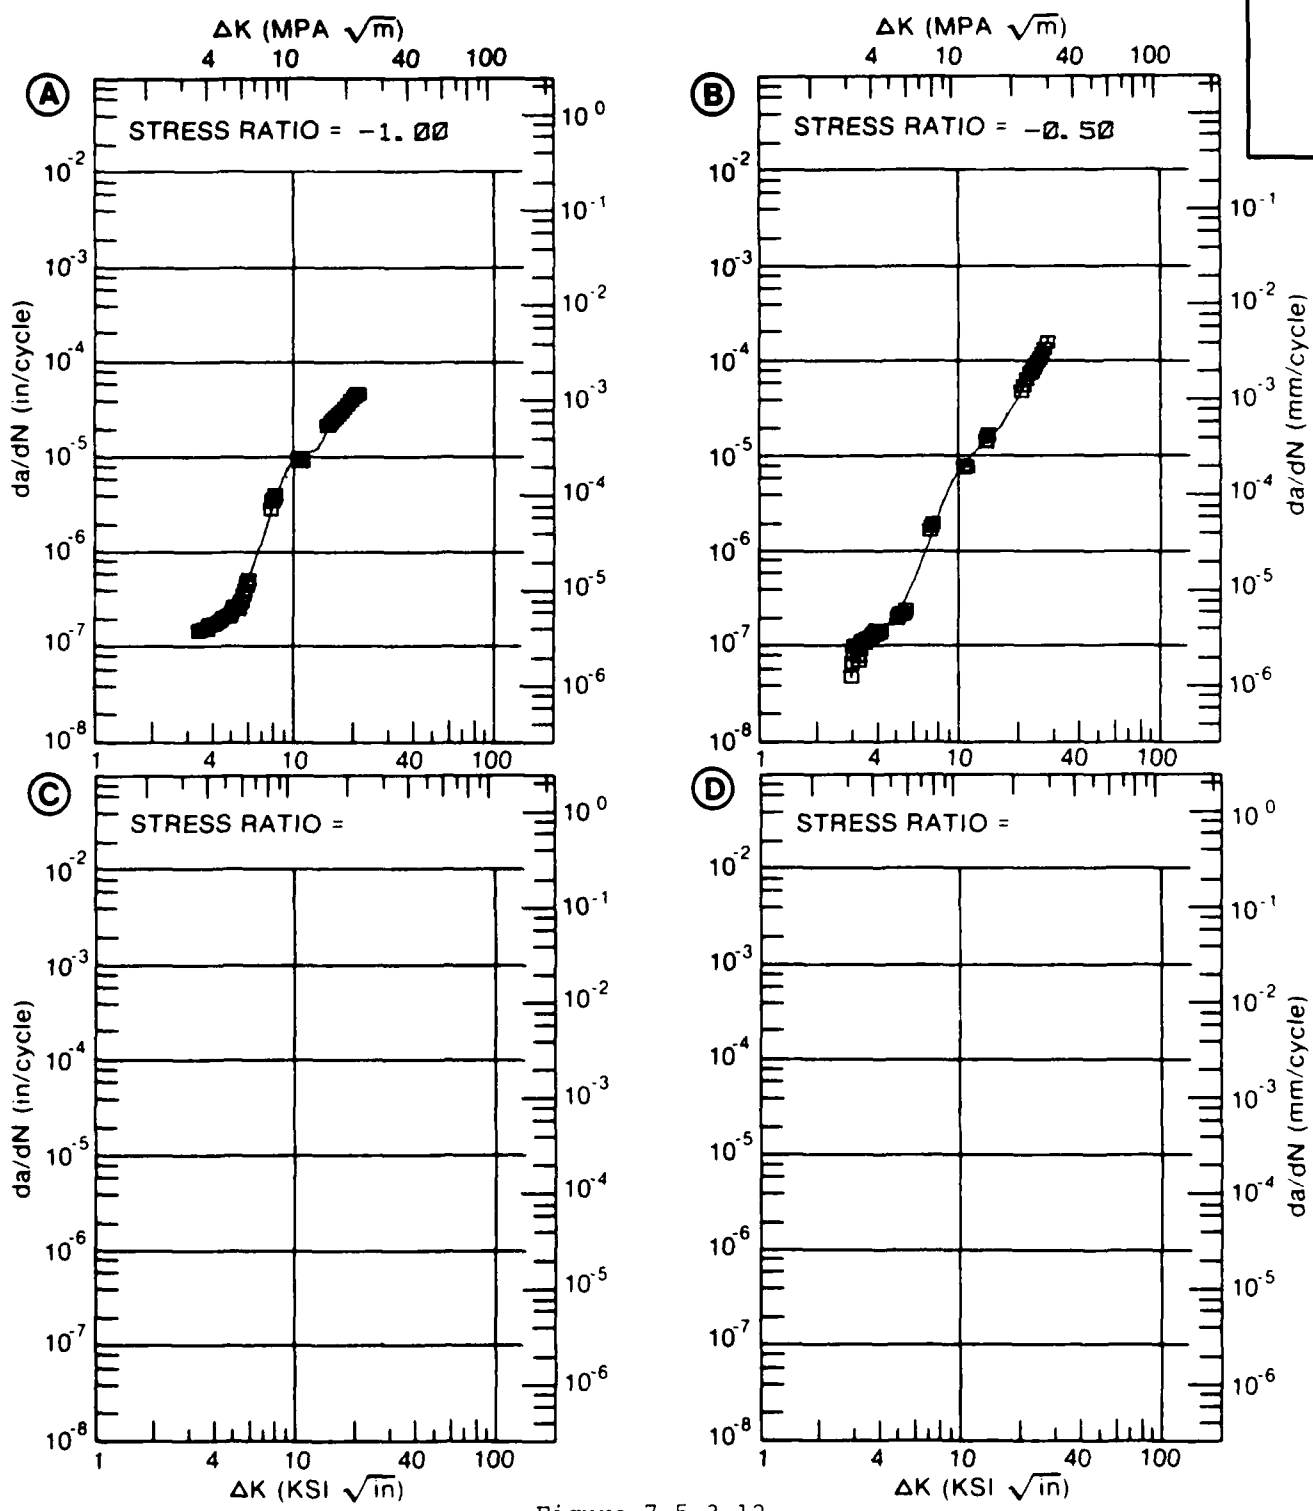


Figure 7.5.3.12

TABLE 7.5.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.13 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.01	R=+0.40	R=+0.60	R=+0.80
DELTA K MIN	A: 5.00	.205			
	B: 3.27		.182		
	C: 5.50			.161	
	D: 3.34				.316
	3.50		.177	.161	.327
	4.00		.235	.250	.520
	5.00	.205	.704	.878	1.71
	6.00	.521	2.00	2.15	3.89
	7.00	1.57	3.99	4.08	7.00
	8.00	3.19	6.24	6.60	11.4
	9.00	5.11	8.73	9.77	18.8
	10.00	7.09	11.7	13.8	33.2
	13.00	13.0	24.0	33.9	175.
	16.00	20.9	44.8	78.0	
	20.00	39.8			
	25.00	91.2			
	30.00	205.			
	35.00	389.			
DELTA K MAX	A: 39.11	546.			
	B: 17.04		55.1		
	C: 18.46			153.	
	D: 14.85				309.
ROOT MEAN SQUARE PERCENT ERROR		14.88	7.66	6.94	8.45
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	1	1	1	1
	1.25-2.0				
	>2.0				

CONDITION/HT: T351
 FORM: PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00- 10.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 54.5 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.241- 0.242"
 SPECIMEN WIDTH: 8.995- 9.000"
 REFERENCES: DA001

ALUM.
ALLOY

2024

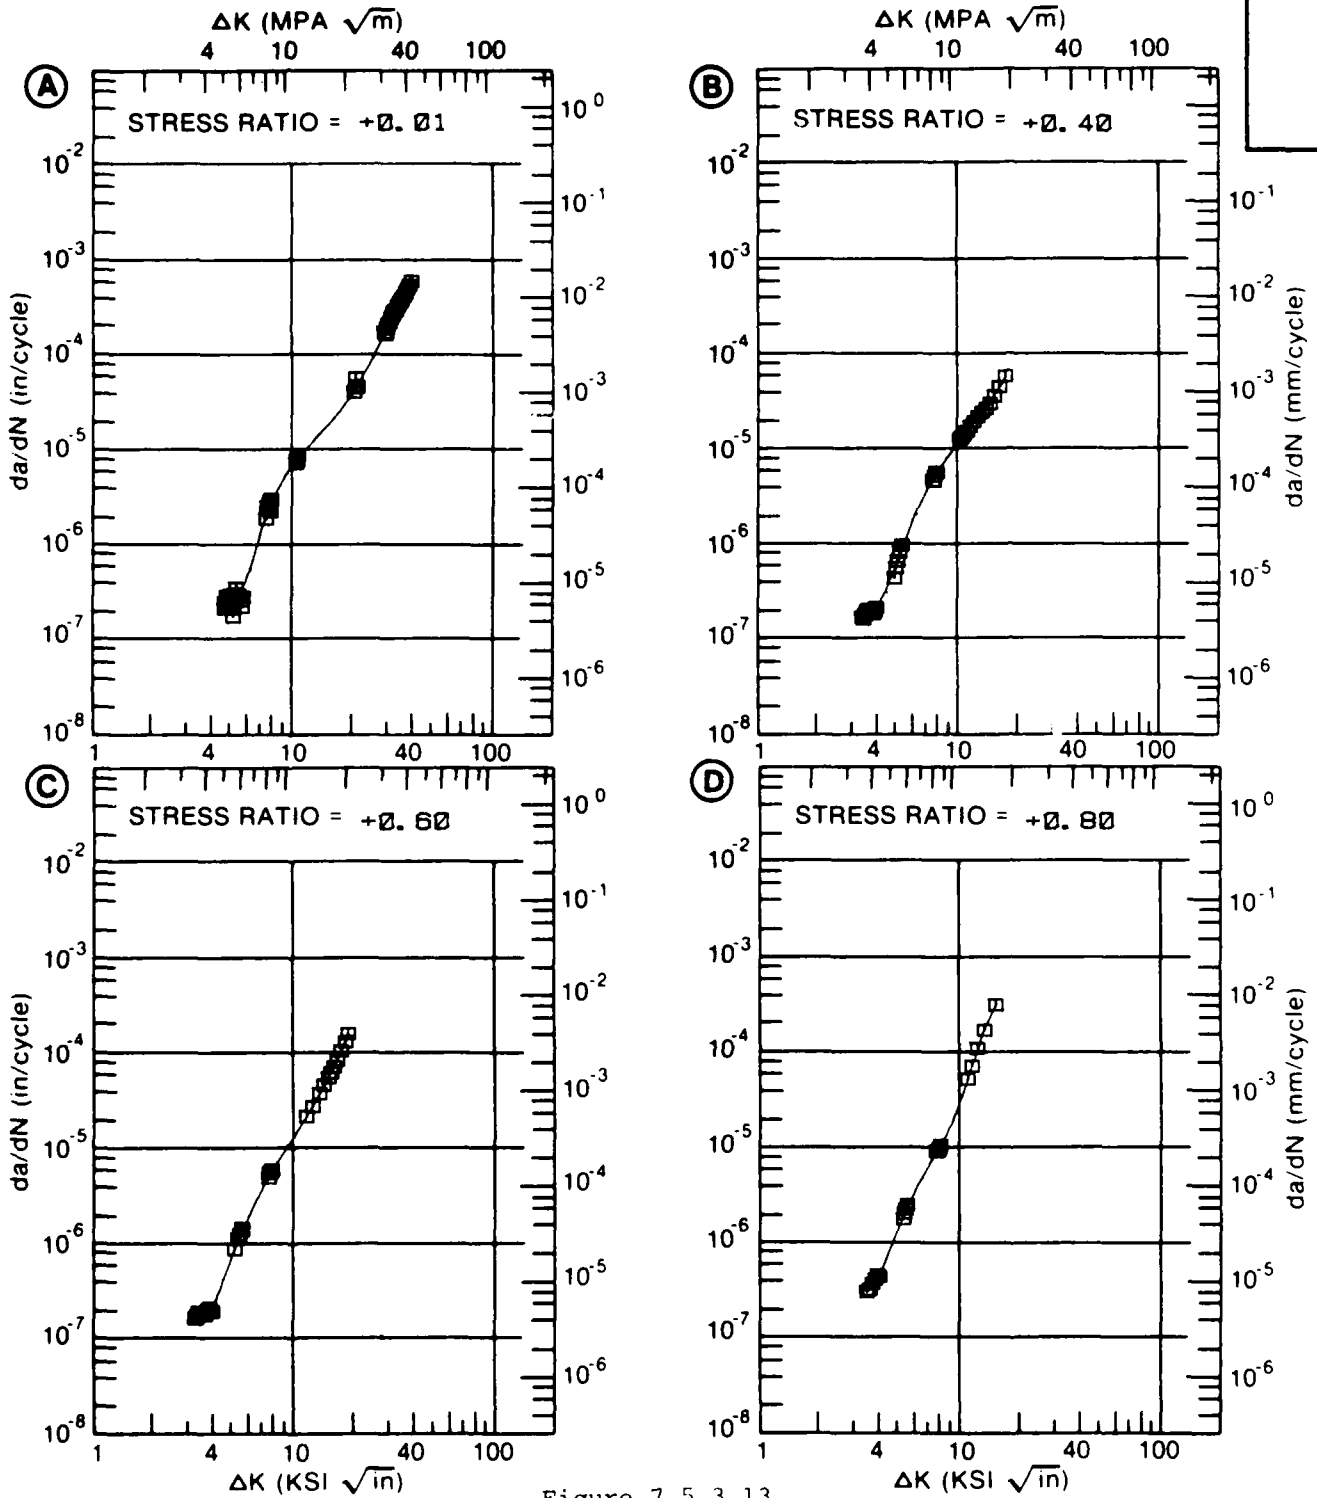


Figure 7.5.3.13

TABLE 7.5.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.14 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: - 65F, AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.00			
DELTA K	A: 27.49	176.			
MIN	B:				
	C:				
	D:				
	30.00	261.			
	35.00	503.			
	40.00	866.			
	50.00	2098.			
	60.00	4367.			
DELTA K	A: 60.32	4463.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		7.04			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00- 2.00 HZ
 ENVIRONMENT: - 65° F, AIR

YIELD STRENGTH: 56.9 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.259"
 SPECIMEN WIDTH: 12.002"
 REFERENCES: DA001

ALUM.
ALLOY

2024

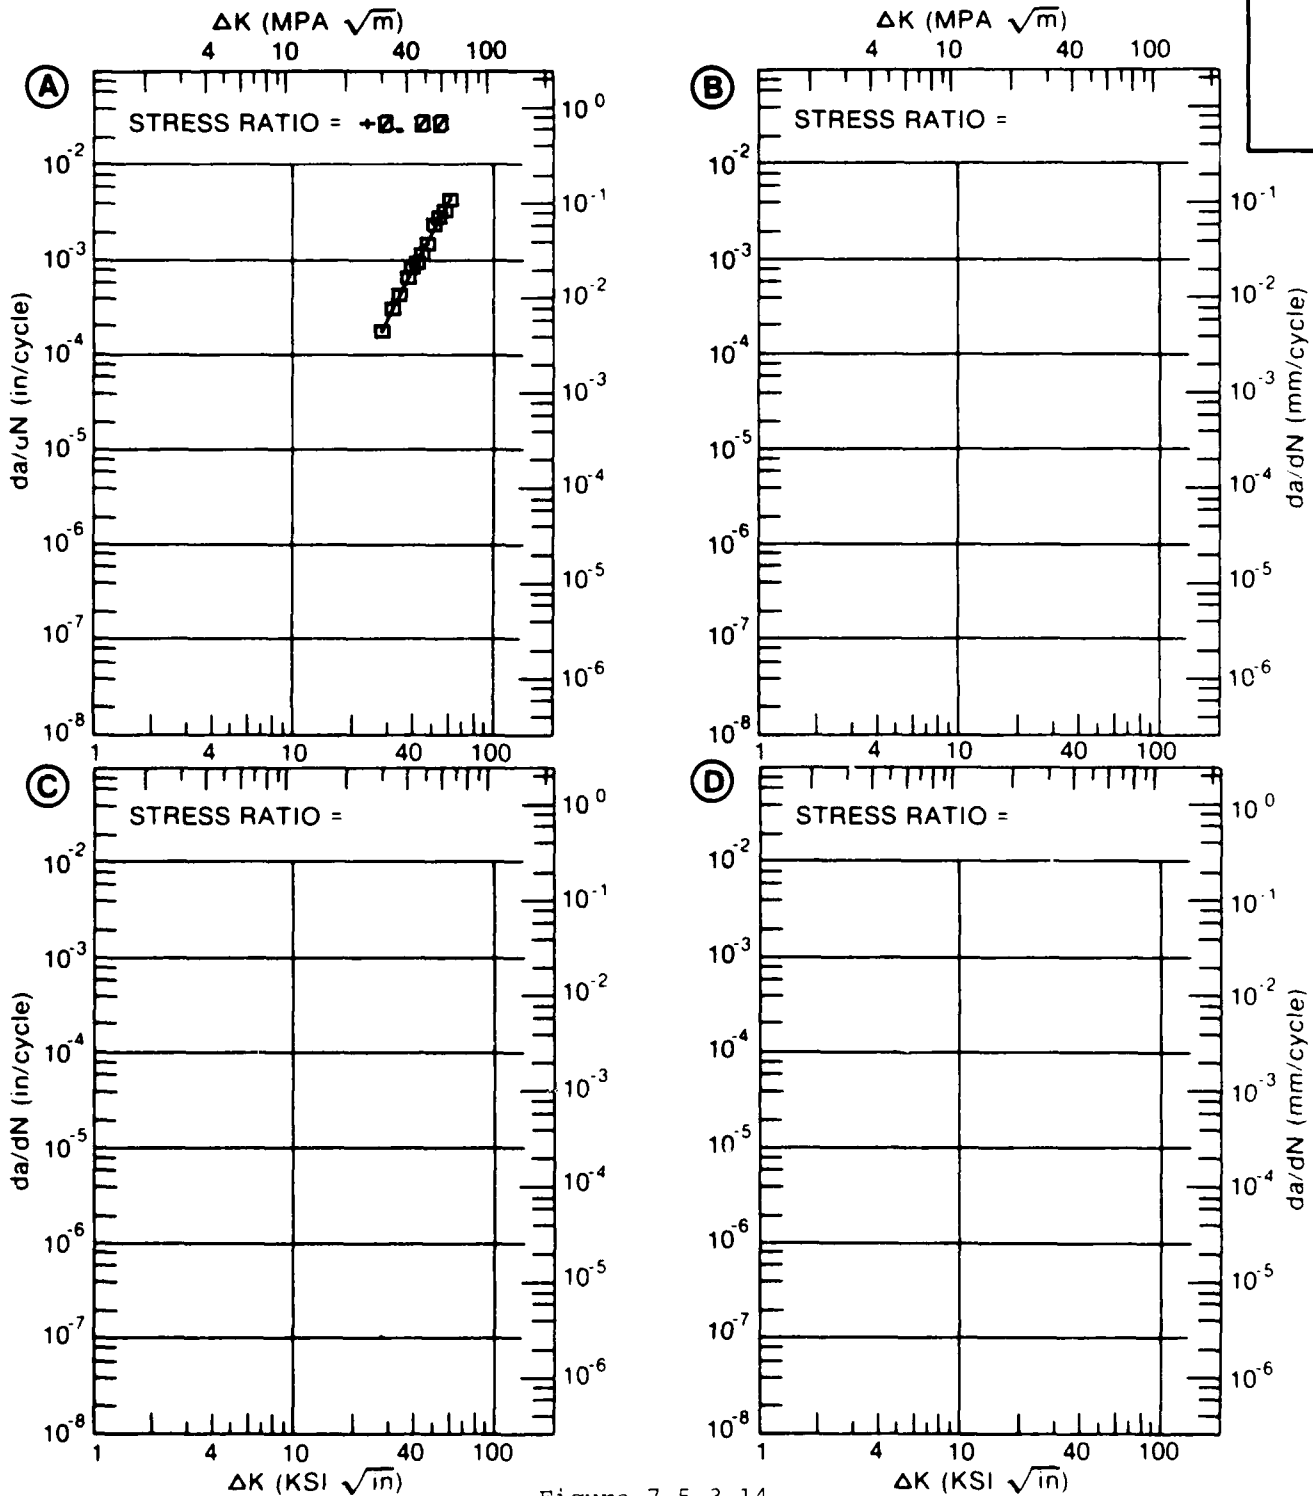


Figure 7.5.3.14

TABLE 7.5.3.15

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.15 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.40	R=+0.80	
DELTA K	A: 4.49 :	.109			
MIN	B: 3.67 :		.219		
	C: 4.71 :			1.06	
	D:				
	4.00 :		.227		
	5.00 :	.156	.478	1.41	
	6.00 :	.244	1.30	3.08	
	7.00 :	.792	3.07	5.46	
	8.00 :		5.65		
	9.00 :		7.80		
DELTA K	A: 7.41 :	1.79			
MAX	B: 9.80 :		8.28		
	C: 7.53 :			7.04	
	D:				
ROOT MEAN SQUARE		15.52	12.18	2.83	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 5.00- 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 56.9 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.188- 0.192"
 SPECIMEN WIDTH: 3.999- 4.003"
 REFERENCES: DA001

ALUM.
ALLOY

2024

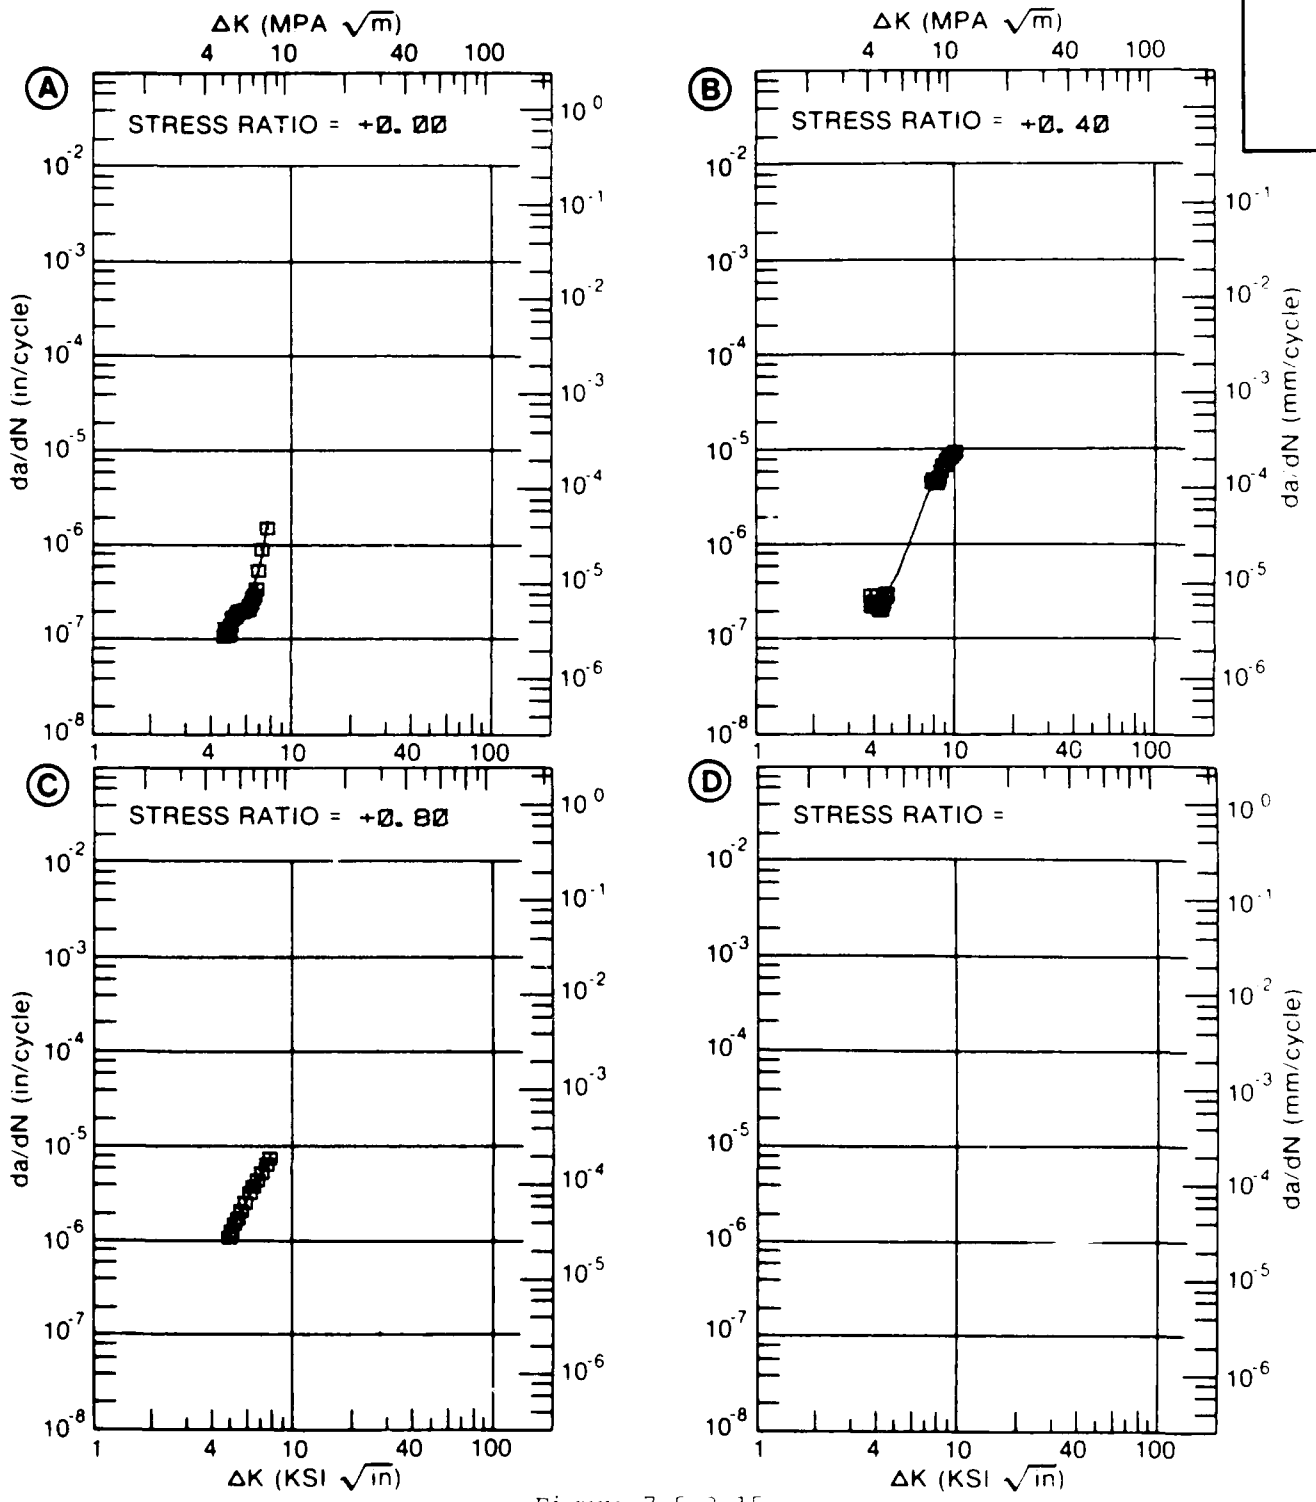


Figure 7.5.3.15

TABLE 7.5.3.16

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.16 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-1.00	R=+0.00	R=+0.40	R=+0.80
DELTA K MIN	A: 11.83	12.2	119.	17.9	2.68
	B: 23.72				
	C: 10.67				
	D: 5.32				
	6.00				4.16
	7.00				8.61
	8.00				17.7
	9.00				34.2
	10.00				60.9
	13.00	17.5		28.0	204.
	16.00	36.2		70.2	
	20.00	74.6		232.	
	25.00	159.	148.		
	30.00	325.	306.		
	35.00	658.	552.		
	40.00		924.		
	50.00		2324.		
DELTA K MAX	A: 38.29	1051.	2877.	444.	275.
	B: 52.44				
	C: 22.69				
	D: 14.31				
ROOT MEAN SQUARE		17.03	3.77	7.82	9.27
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	2	1	1	1
	1.25-2.0				
	>2.0				

CONDITION/HT: T351
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00- 16.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 56.9 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.189- 0.261"
 SPECIMEN WIDTH: 11.997- 12.007"
 REFERENCES: DA001

ALUM. ALLOY
2024

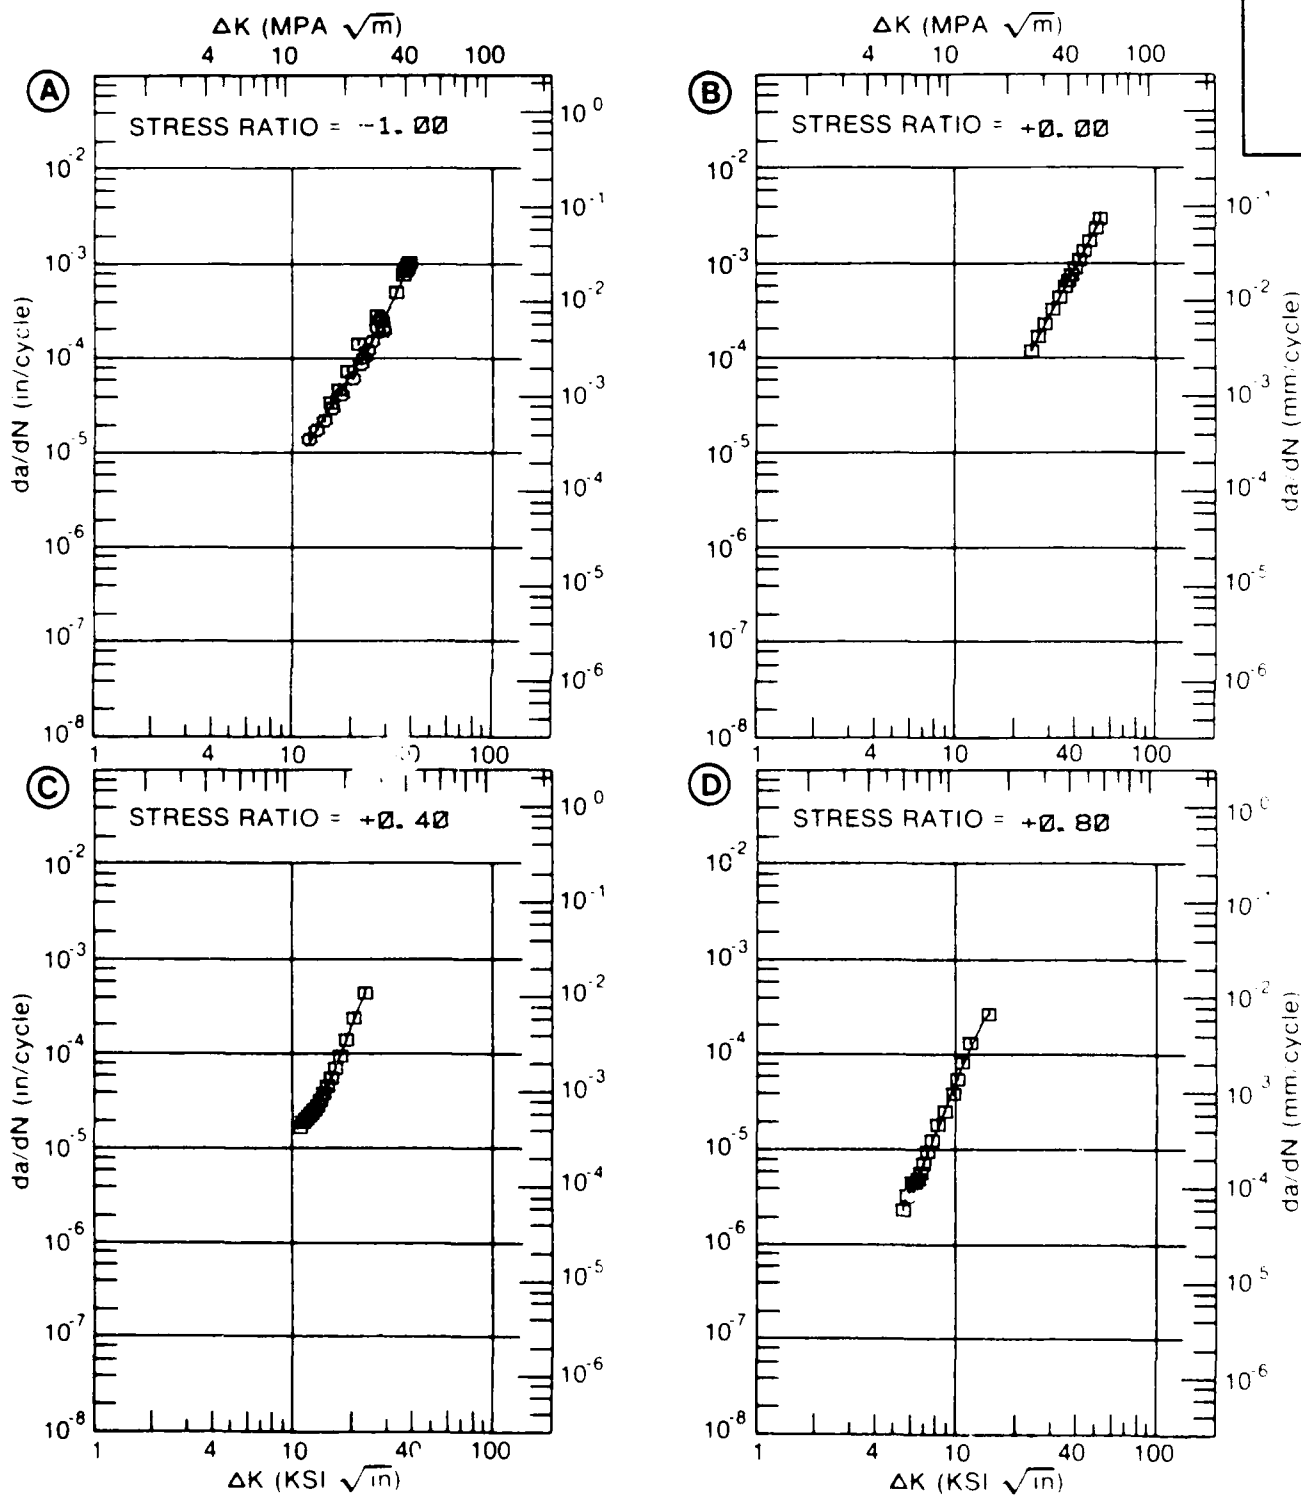


Figure 7.5.3.16

TABLE 7.5.3.17

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.17 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T351
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 12.37	14.6			
MIN	B:				
	C:				
	D:				
	13.00	17.5			
	16.00	29.5			
	20.00	55.0			
DELTA K	A: 24.93	209.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 13.67
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T351
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 3.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: FR001

ALUM.
ALLOY

2024

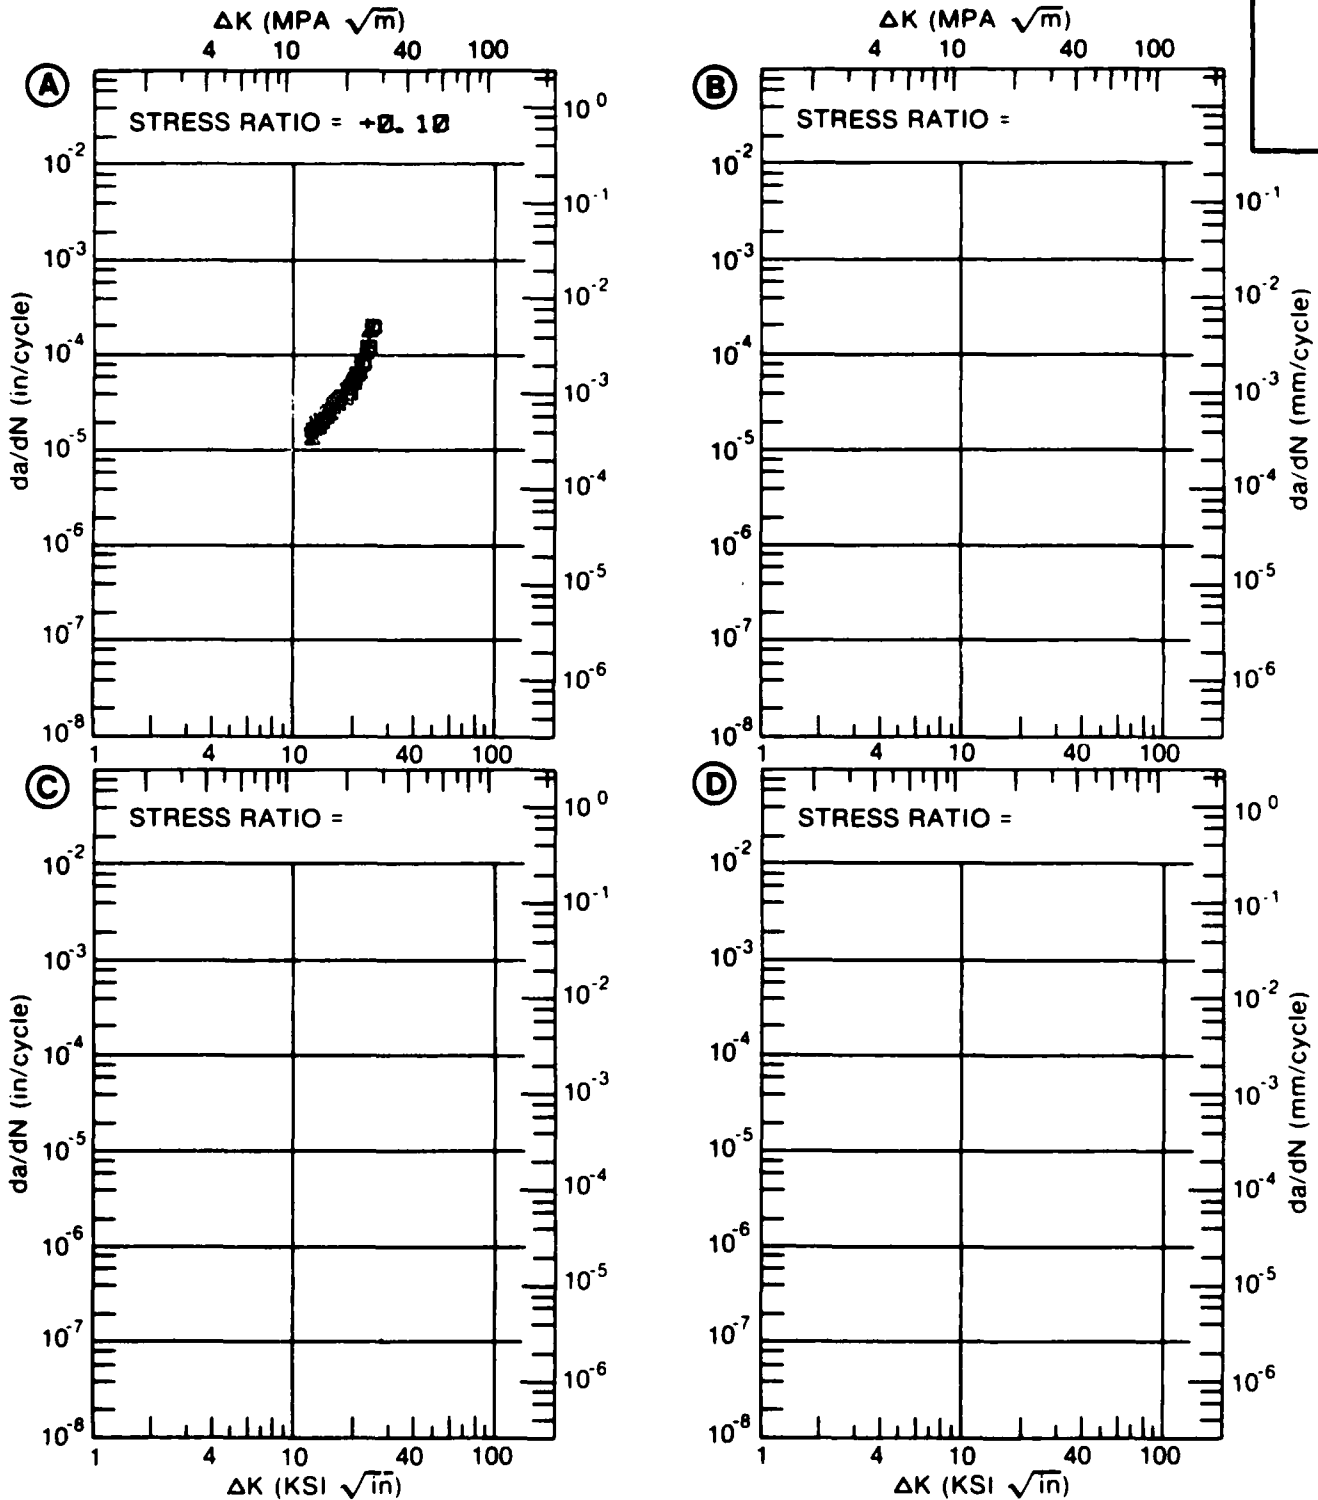


Figure 7.5.3.17

TABLE 7.5.3.18

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.18 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E=+ 200F AIR	E=+ 300F AIR	E=+ 400F AIR
DELTA K MIN	A: 8.19	2.84			
	B: 7.67		3.23		
	C: 6.72			2.15	
	D: 6.52				2.02
	7.00			2.38	2.44
	8.00		3.58	3.50	3.54
	9.00	4.06	4.96	5.14	4.99
	10.00	5.98	6.92	7.43	6.89
	13.00	14.8	17.5	19.2	16.4
	16.00	28.3	37.2	38.6	35.2
	20.00	52.1			
DELTA K MAX	A: 21.86	64.7			
	B: 16.64		42.7		
	C: 19.19			63.7	
	D: 19.04				70.9
ROOT MEAN SQUARE PERCENT ERROR		12.74	10.27	10.95	17.31
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0				

CONDITION/HT: T351
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.01
 FREQUENCY: 20.00 HZ

YIELD STRENGTH: 51.5 KSI
 ULT. STRENGTH: 65.9 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: U0000

ALUM.
ALLOY

2024

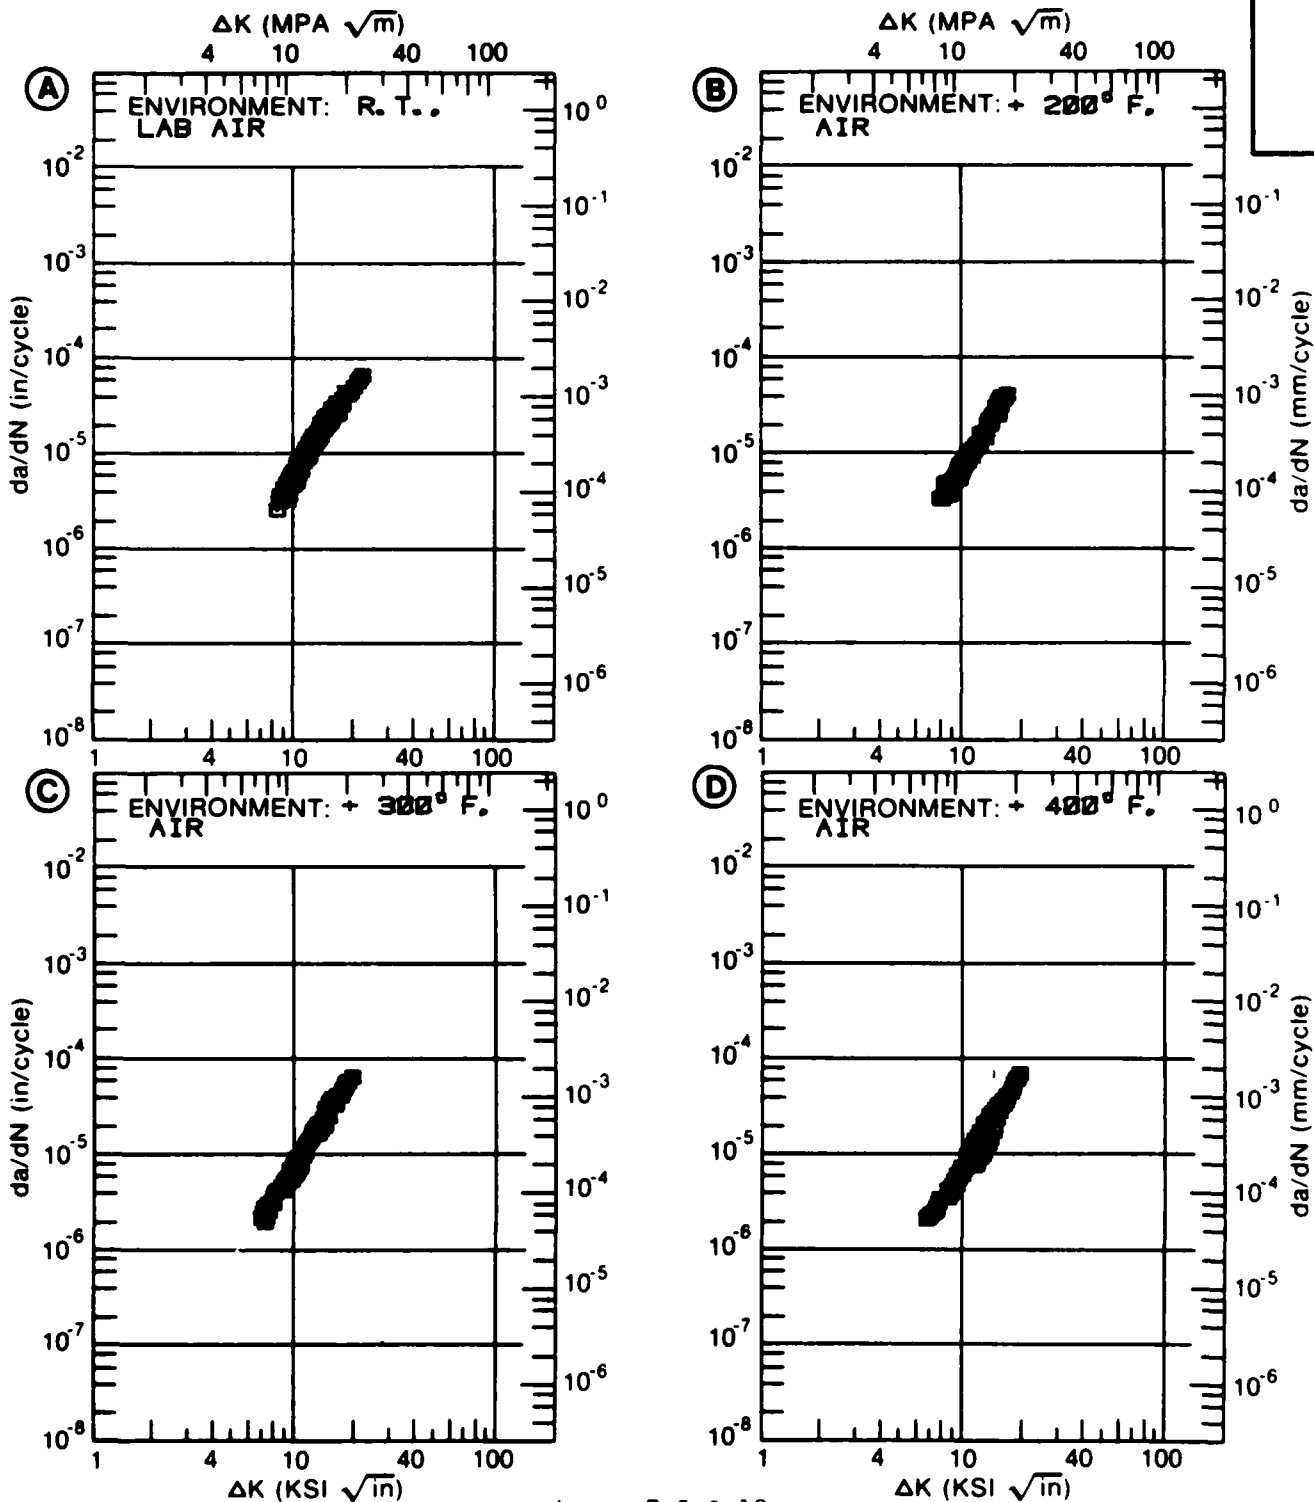


Figure 7.5.3.18

TABLE 7.5.3.19

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.19 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.	E=+ 200F	E=+ 300F	E=+ 400F
		LAB AIR	AIR	AIR	AIR
DELTA K A:	7.96	4.07			
DELTA K B:	6.84		2.95		
MIN C:	6.93			2.44	
D:	6.68				2.73
	7.00		3.11	2.54	3.11
	8.00	4.14	4.37	4.28	4.77
	9.00	6.03	6.18	6.47	7.27
	10.00	8.62	8.70	9.35	10.6
	13.00	21.4	22.2		
DELTA K A:	13.55	24.5			
MAX B:	13.54		25.8		
C:	11.58			16.5	
D:	11.82				18.5
ROOT MEAN SQUARE		7.41	21.25	5.04	4.60
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 20.00 HZ

YIELD STRENGTH: 51.5 KSI
 ULT. STRENGTH: 65.9 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: UD009

ALUM.
ALLOY

2024

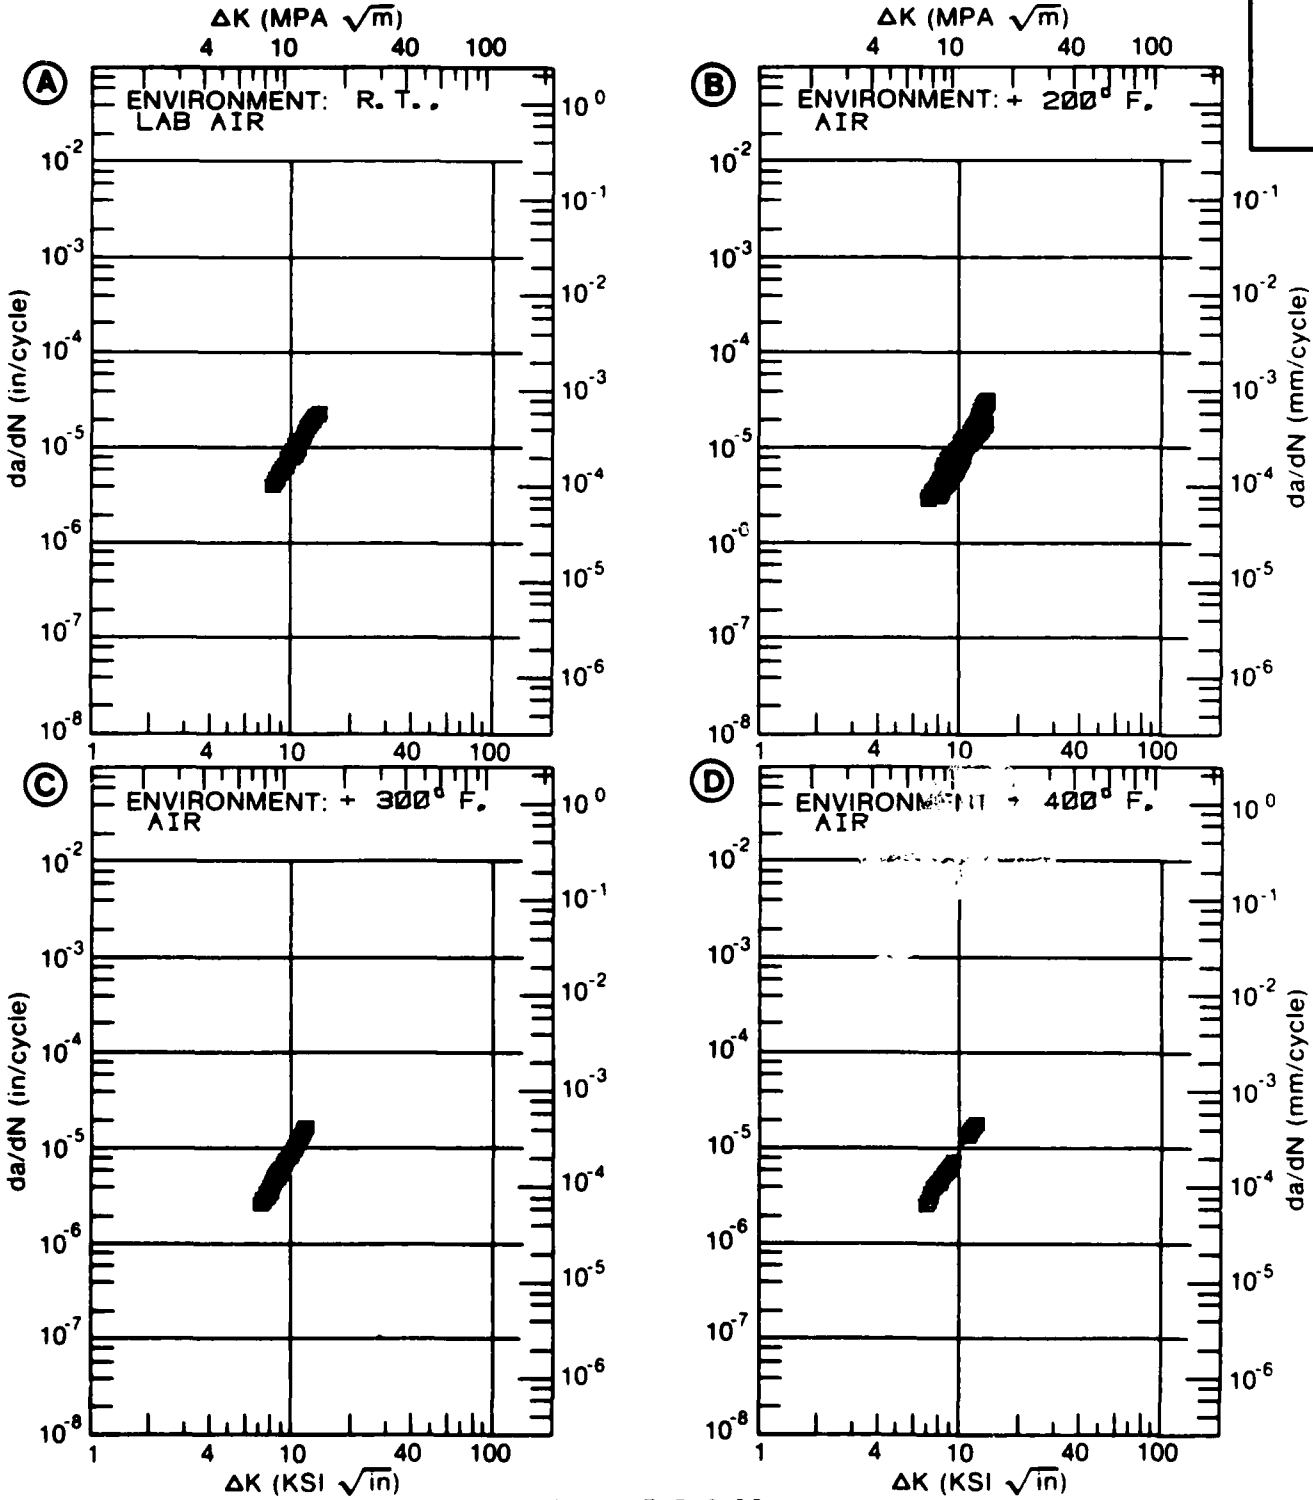


Figure 7.5.3.19

TABLE 7.5.3.20

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.20 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T.	E=+ 200F	E=+ 300F	E=+ 400F
		LAB AIR	AIR	AIR	AIR
DELTA K	A: 6.16 :	1.90			
MIN	B: 5.35 :		1.66		
	C: 5.60 :			1.47	
	D: 5.49 :				1.54
	6.00 :		2.11	1.94	2.17
	7.00 :	2.92	3.21	3.48	3.78
	8.00 :	4.67	4.93	5.65	5.96
	9.00 :	7.12	7.42	8.54	8.80
	10.00 :	10.4	10.8	12.3	12.4
	13.00 :	24.8	27.2	29.7	30.3
	16.00 :	43.5	50.2	59.8	
DELTA K	A: 16.29 :	45.4			
MAX	B: 17.32 :		60.7		
	C: 16.43 :			65.5	
	D: 15.83 :				62.8
ROOT MEAN SQUARE		14.89	16.14	9.06	11.01
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.30
 FREQUENCY: 20.00 HZ

YIELD STRENGTH: 51.5 KSI
 ULT. STRENGTH: 65.9 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: UD009

ALUM. ALLOY
2024

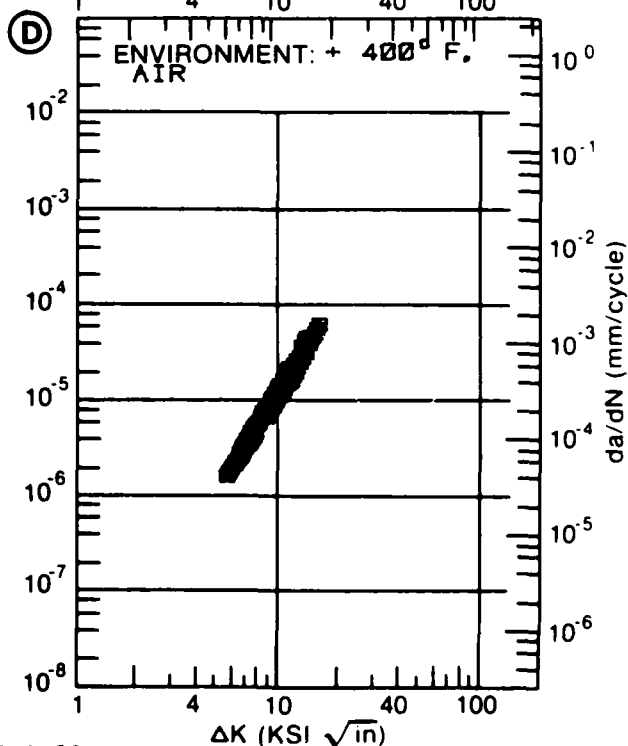
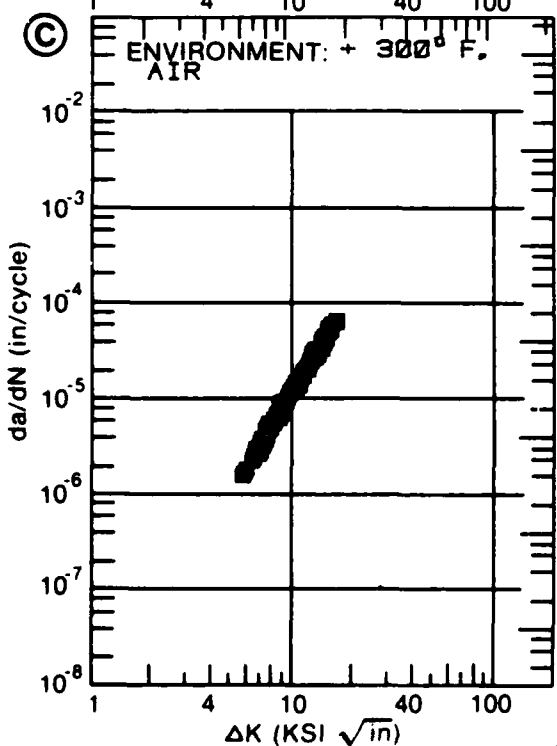
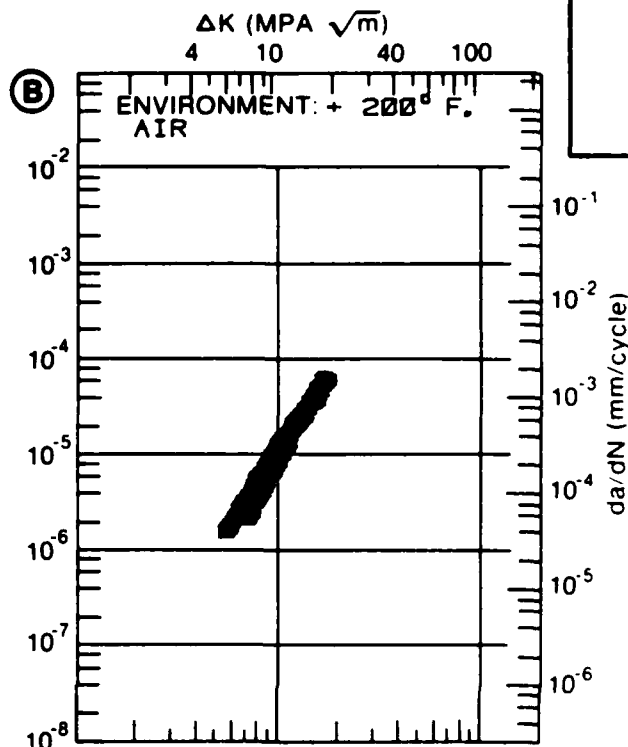
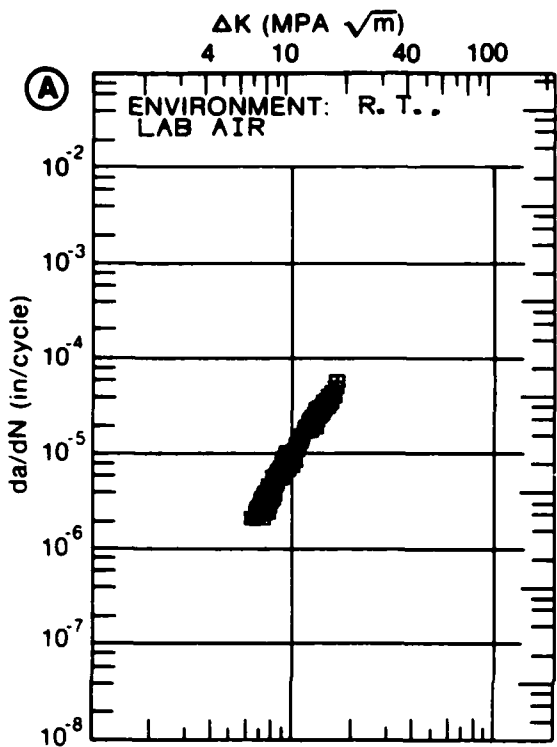


Figure 7.5.3.20

TABLE 7.5.3.21

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.21 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E=+ 200F AIR	E=+ 300F AIR	E=+ 400F AIR
DELTA K	A: 5.77	1.92			
MIN	B: 5.60		1.59		
	C: 5.46			1.62	
	D: 4.93				1.41
	5.00				1.47
	6.00	2.25	2.09	2.35	2.57
	7.00	3.94	3.77	4.14	4.08
	8.00	6.13	6.13	6.55	6.27
	9.00	9.06	9.31	9.66	9.55
	10.00	13.1	13.5	13.6	14.6
	13.00		33.8	31.7	
DELTA K	A: 12.59	35.0			
MAX	B: 13.83		42.2		
	C: 13.79			38.6	
	D: 12.26				39.4
ROOT MEAN SQUARE		15.96	7.06	7.78	17.54
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.50
 FREQUENCY: 20.00 HZ

YIELD STRENGTH: 51.5 KSI
 ULT. STRENGTH: 65.9 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: UD009

ALUM.
 ALLOY
 2024

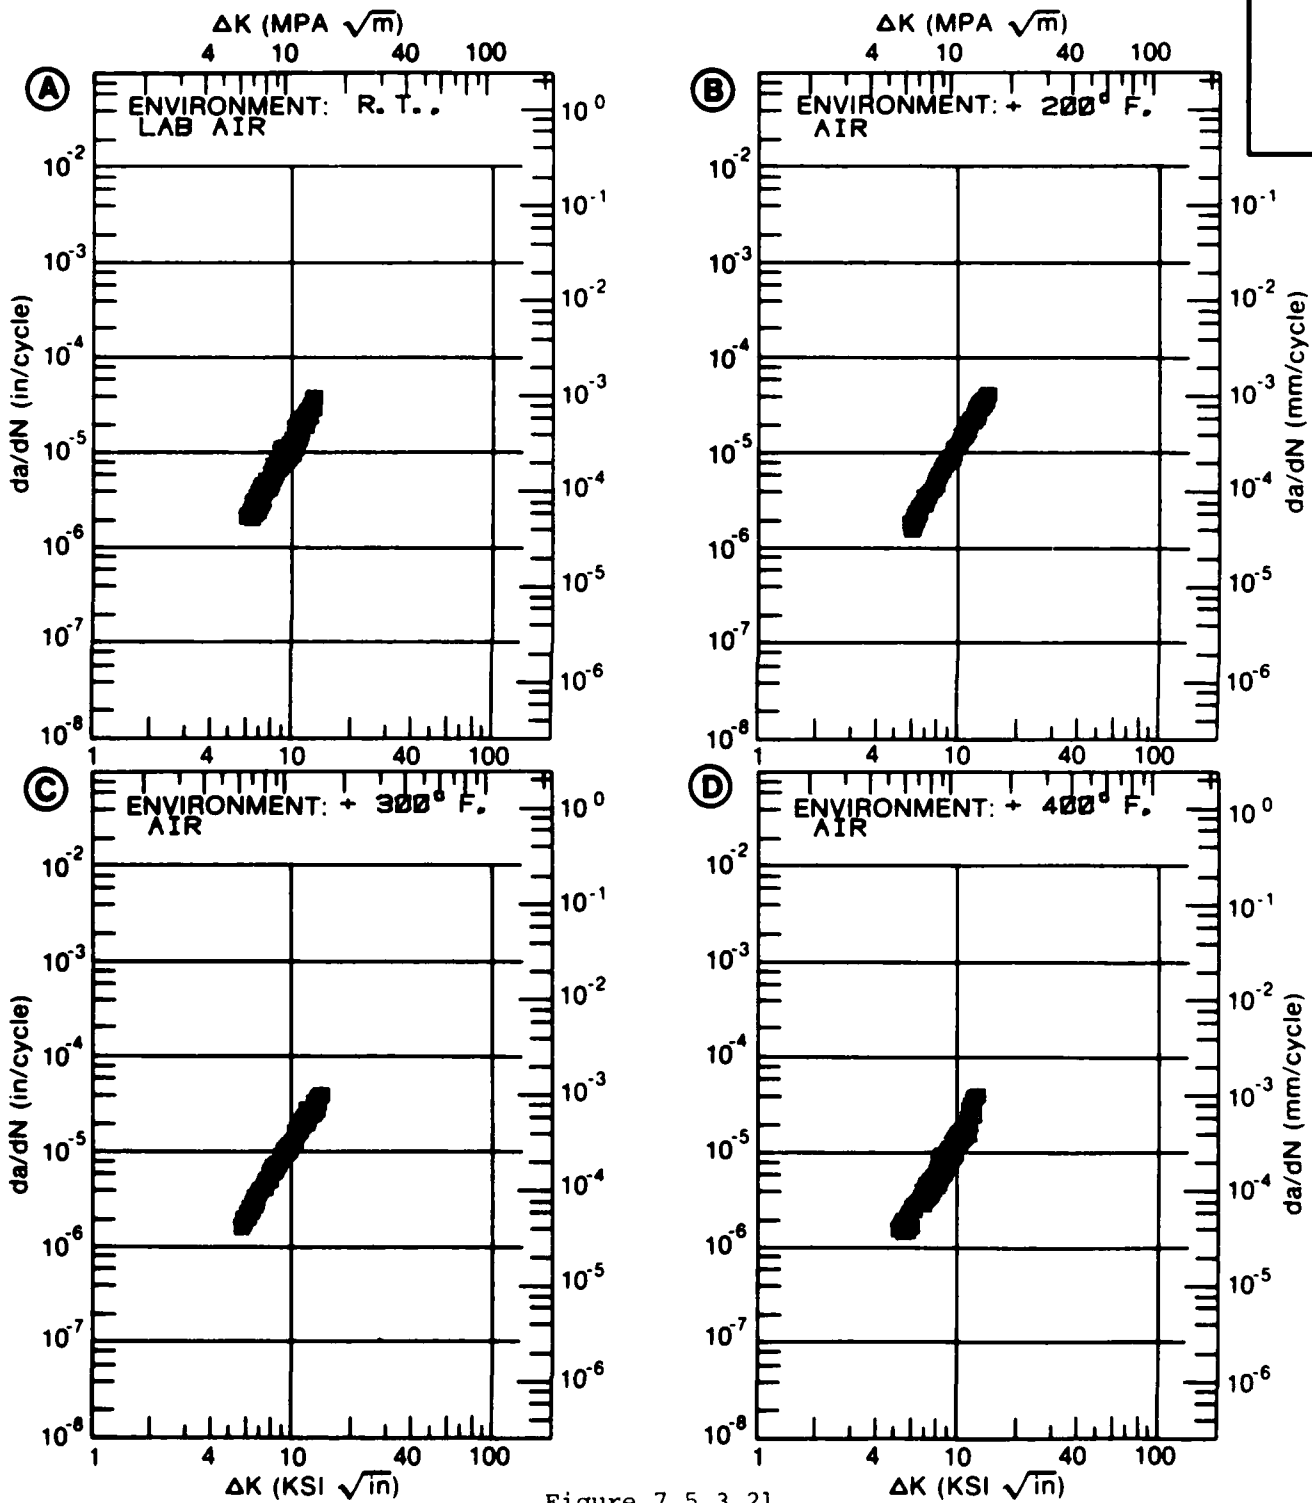


Figure 7.5.3.21

TABLE 7.5.3.22

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.22 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T.	E=+ 200F	E=+ 300F	E=+ 400F
		LAB AIR	AIR	AIR	AIR
DELTA K	A: 5.67	1.67			
MIN	B: 6.63		3.96		
	C: 6.14			3.03	
	D: 4.18				1.05
	5.00				1.56
	6.00	2.18			2.85
	7.00	4.10	4.44	4.62	5.10
	8.00	6.60	6.71	7.24	8.47
	9.00	9.89	10.2	10.9	12.8
	10.00	14.4	14.3	15.6	17.6
DELTA K	A: 10.96	20.5			
MAX	B: 10.11		14.7		
	C: 10.71			19.8	
	D: 10.12				18.2
ROOT MEAN SQUARE		6.39	5.54	6.01	15.04
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: 0.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.60
 FREQUENCY: 20.00 HZ

YIELD STRENGTH: 51.5 KSI
 ULT. STRENGTH: 65.9 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: UD009

ALUM.
ALLOY

2024

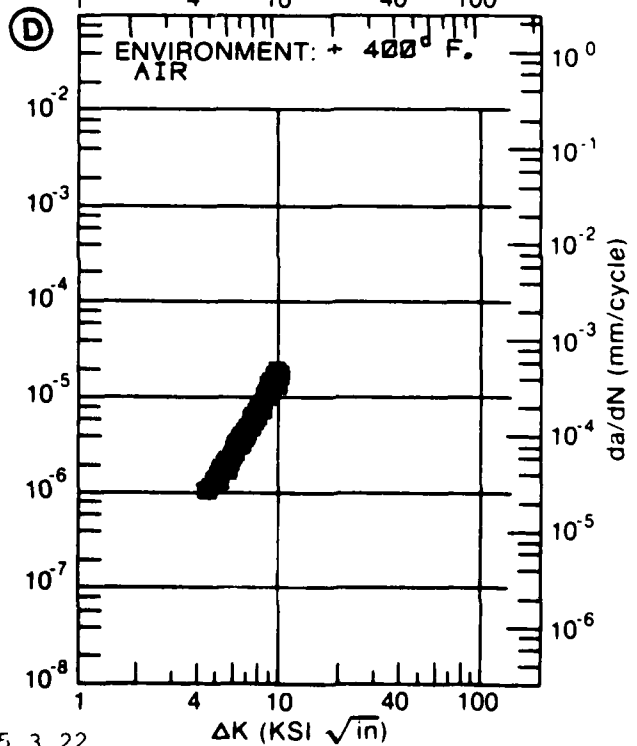
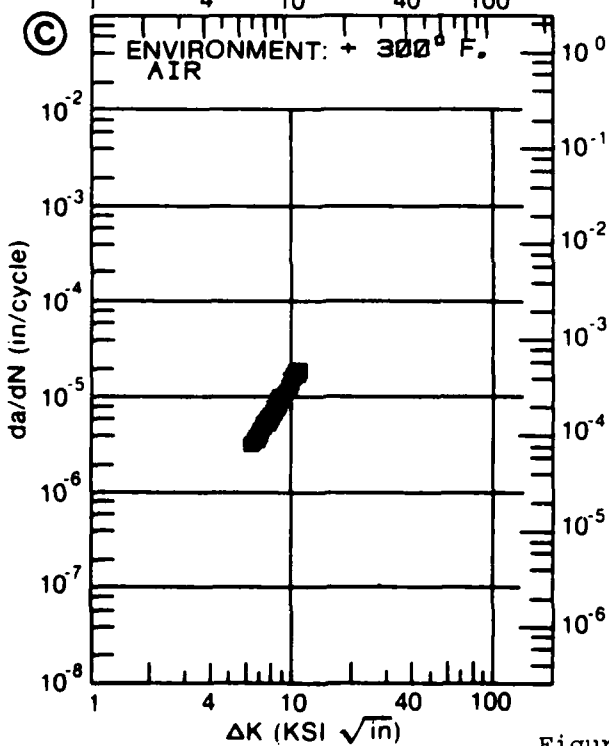
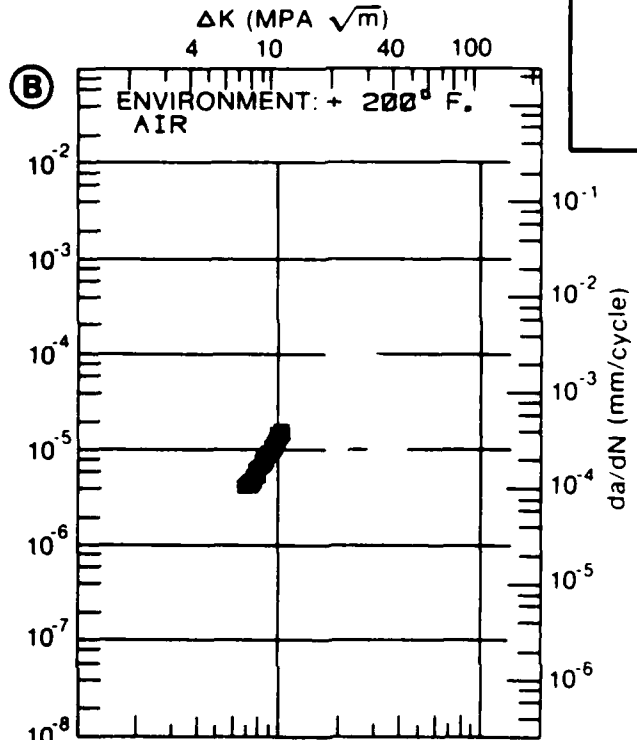
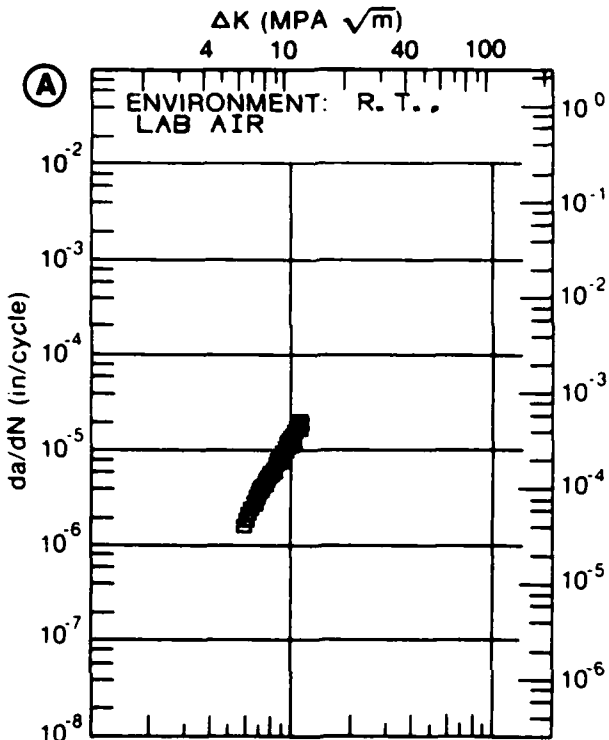


Figure 7.5.3.22

TABLE 7.5.3.23

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.23 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 5.32	.130			
MIN	B:				
	C:				
	D:				
	6.00	.411			
	7.00	1.34			
	8.00	2.97			
	9.00	5.22			
	10.00	7.88			
	13.00	17.0			
	16.00	27.7			
DELTA K	A: 19.53	45.9			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		18.92			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25 1				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T351
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 25.00 HZ

YIELD STRENGTH: 54.4 KSI
 ULT. STRENGTH: 69.3 KSI
 SPECIMEN THK: 0.248"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: AL002

ALUM.
ALLOY

2024

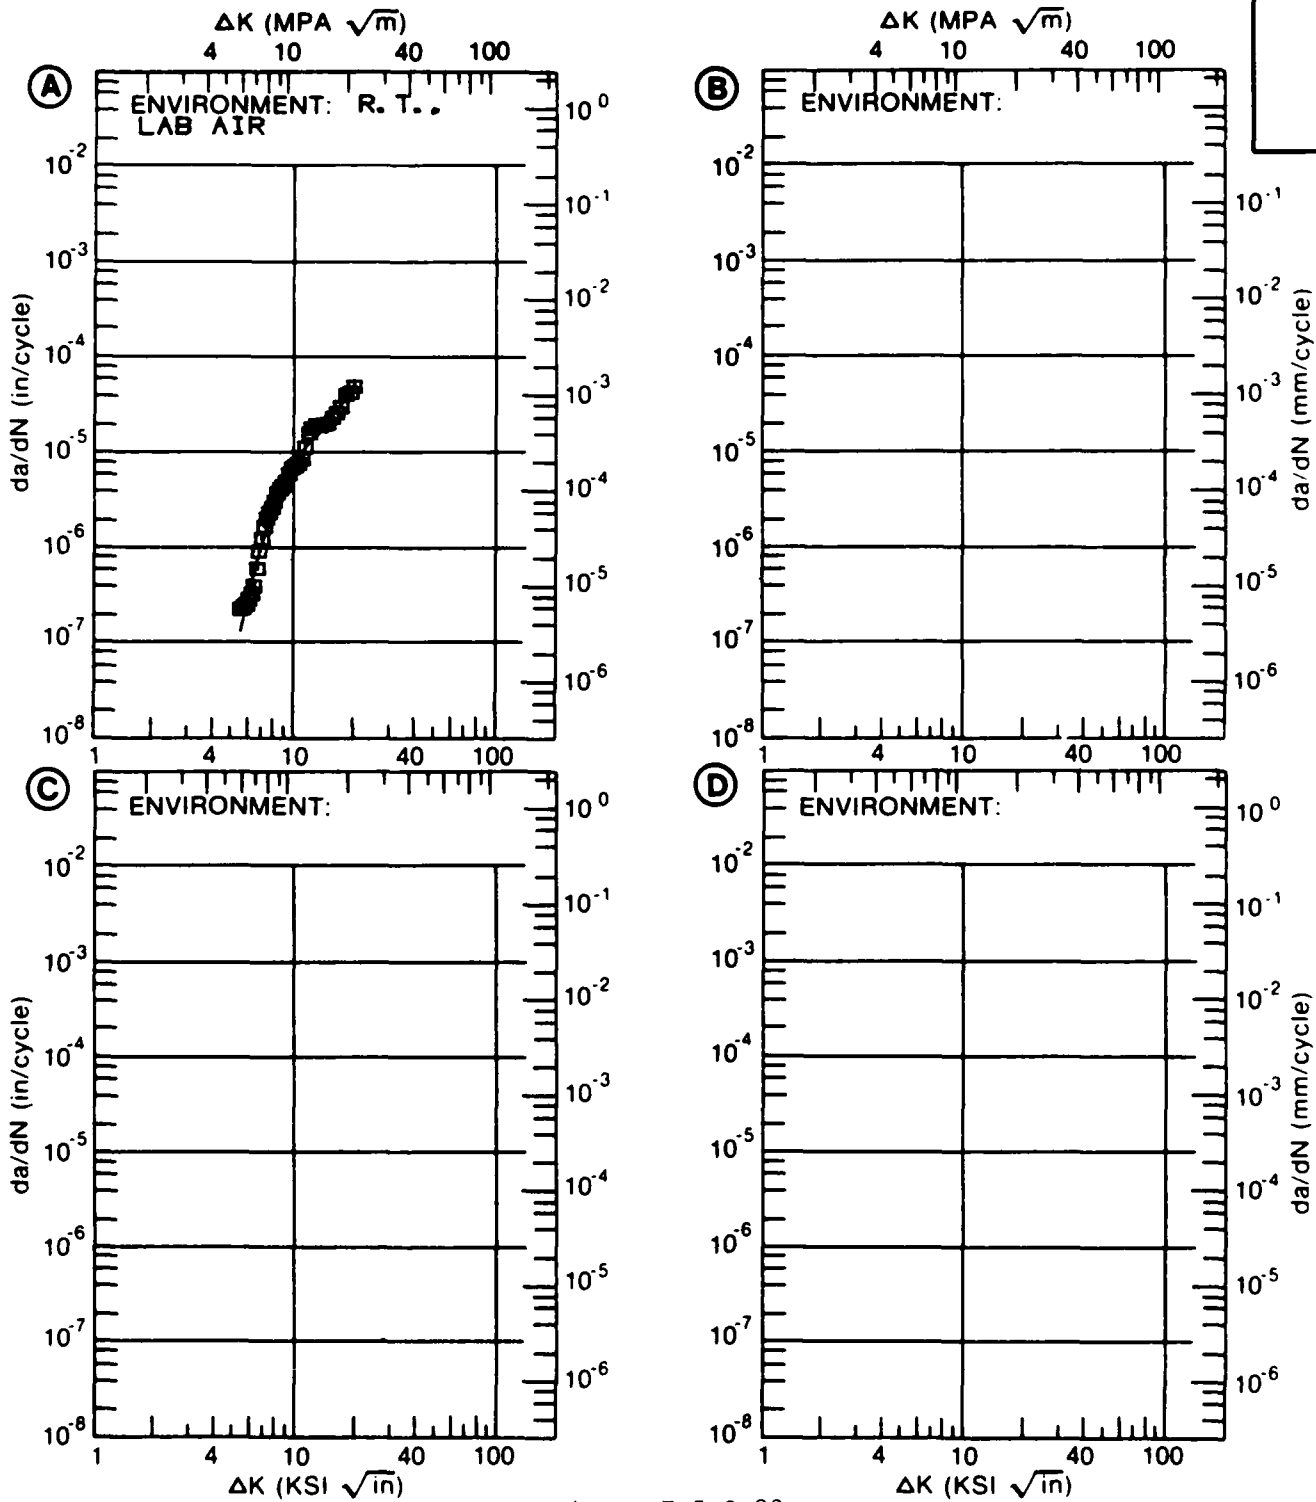


Figure 7.5.3.23

TABLE 7.5.3.24

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.24 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T351					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.			
DELTA K MIN	A: 3.11	.085			
	B: 5				
	C:				
	D:				
	3.50	.150			
	4.00	.183			
	5.00	.356			
	6.00	1.02			
	7.00	2.61			
	8.00	5.12			
	9.00	7.96			
	10.00	10.8			
	13.00	20.2			
	16.00	36.3			
	20.00	96.4			
DELTA K MAX	A: 24.63	138.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		18.66			
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	0.5-0.8	0.8-1.25	1.25-2.0	>2.0
			2		

CONDITION/HT: T351
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 25.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.249"
 SPECIMEN WIDTH: 2.546"
 REFERENCES:AL010

ALUM.
ALLOY

2024

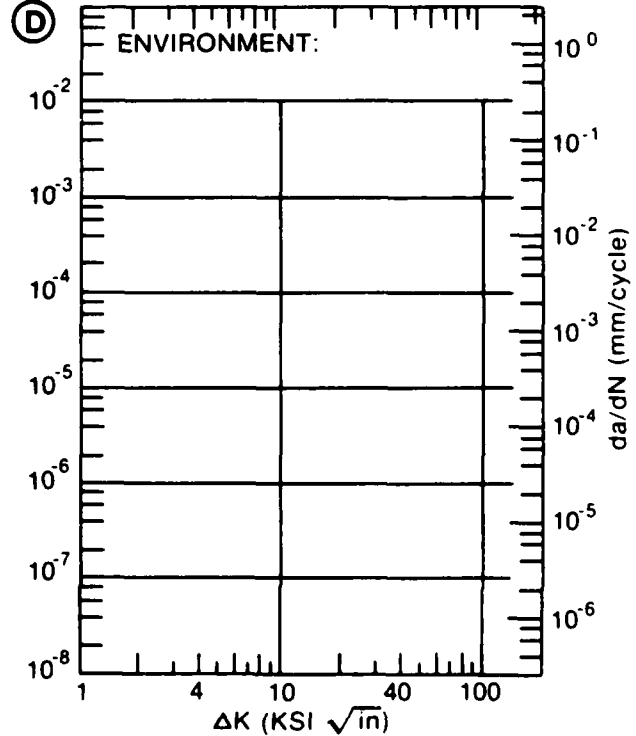
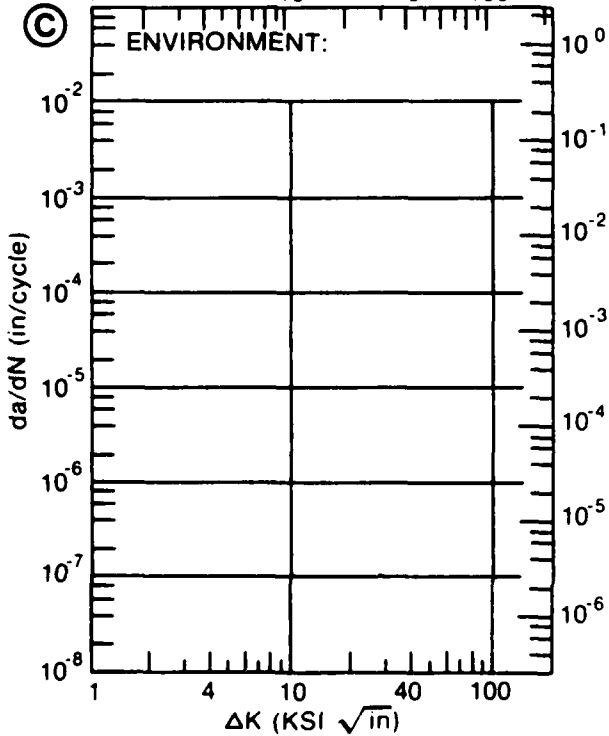
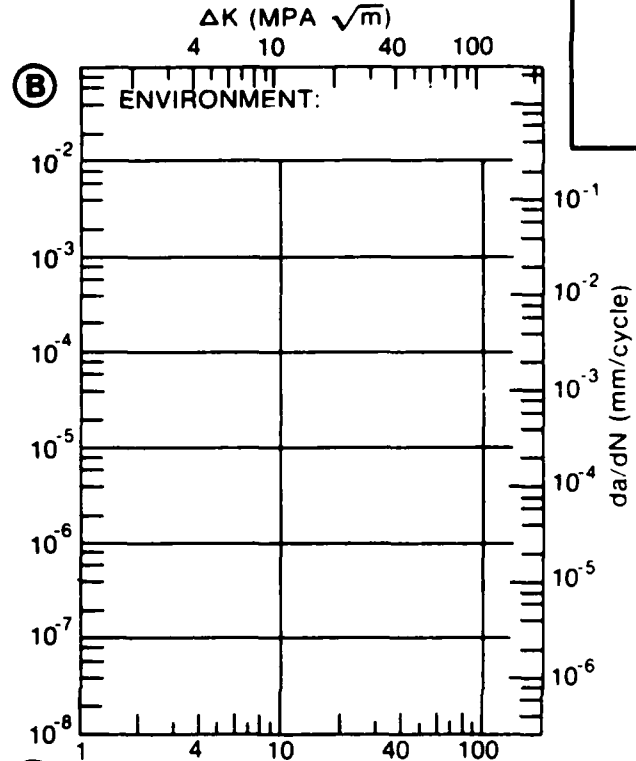
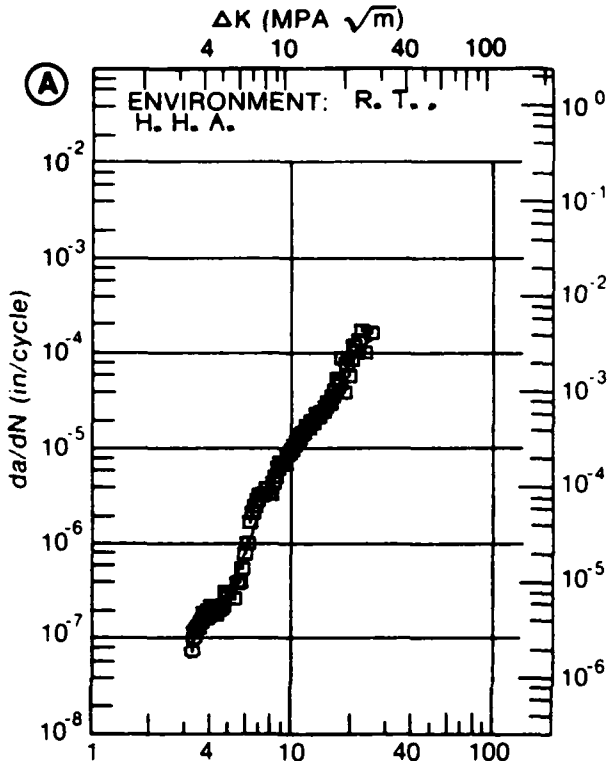


Figure 7.5.3.24

TABLE 7.5.3.25

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.25 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 2024
CONDITION: T351

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. H. H. A.			
DELTA K A: 3.20	.0726			
MIN B:				
C:				
D:				
3.50	.139			
4.00	.330			
5.00	1.10			
6.00	2.44			
7.00	4.33			
8.00	6.72			
9.00	9.60			
10.00	13.0			
13.00	26.9			
16.00	49.6			
DELTA K A: 16.73	57.1			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 26.03
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	1
RATIO	0.8-1.25	1
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: T351
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 25.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.248- 0.249"
 SPECIMEN WIDTH: 2.545- 2.546"
 REFERENCES: AL010

ALUM. ALLOY
2024

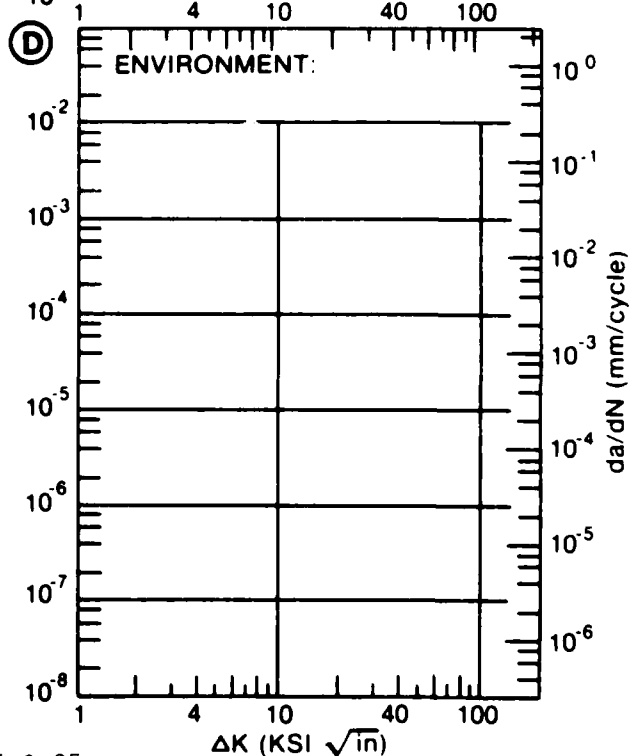
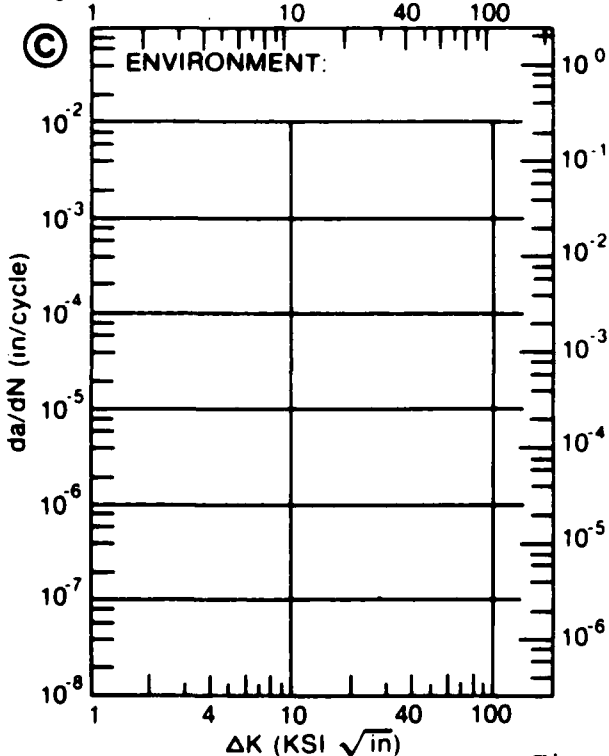
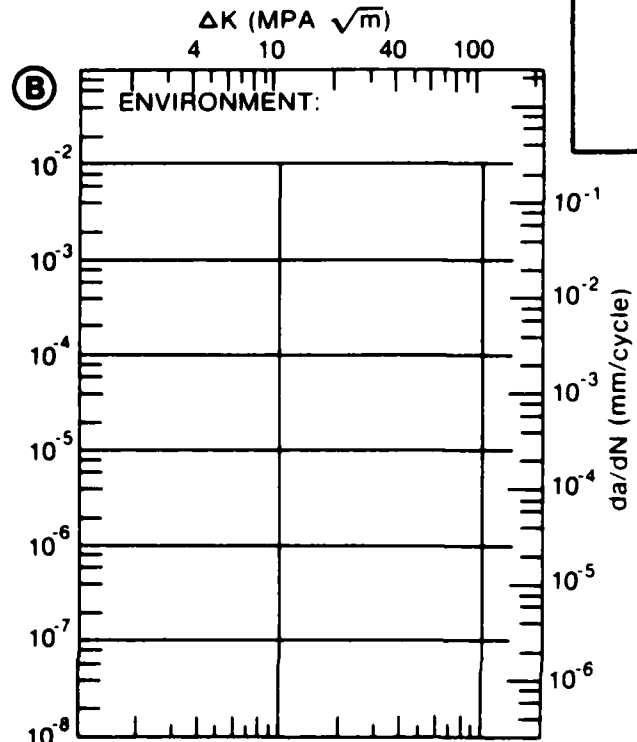
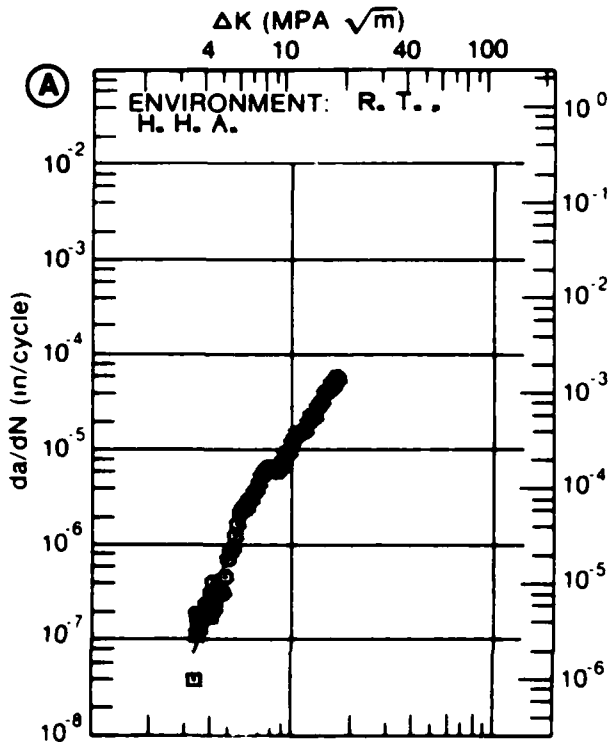


Figure 7.5.3.25

TABLE 7.5.3.26

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.26 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T3511					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		R=+0.05	R=+0.50		
DELTA K MIN	A: 4.39	.0786			
	B: 2.35		.0724		
	C:				
	D:				
	2.50		.0818		
	3.00		.113		
	3.50		.144		
	4.00		.175		
	5.00	.129			
	6.00	.177			
	7.00	.229			
DELTA K MAX	A: 7.98	.361			
	B: 4.49		.204		
	C:				
	D:				
ROOT MEAN SQUARE		31.67	22.07		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T3511
 FORM: EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 9.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 58.7 KSI
 ULT. STRENGTH: 79.3 KSI
 SPECIMEN THK: 0.370"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: BW001

ALUM.
ALLOY

2024

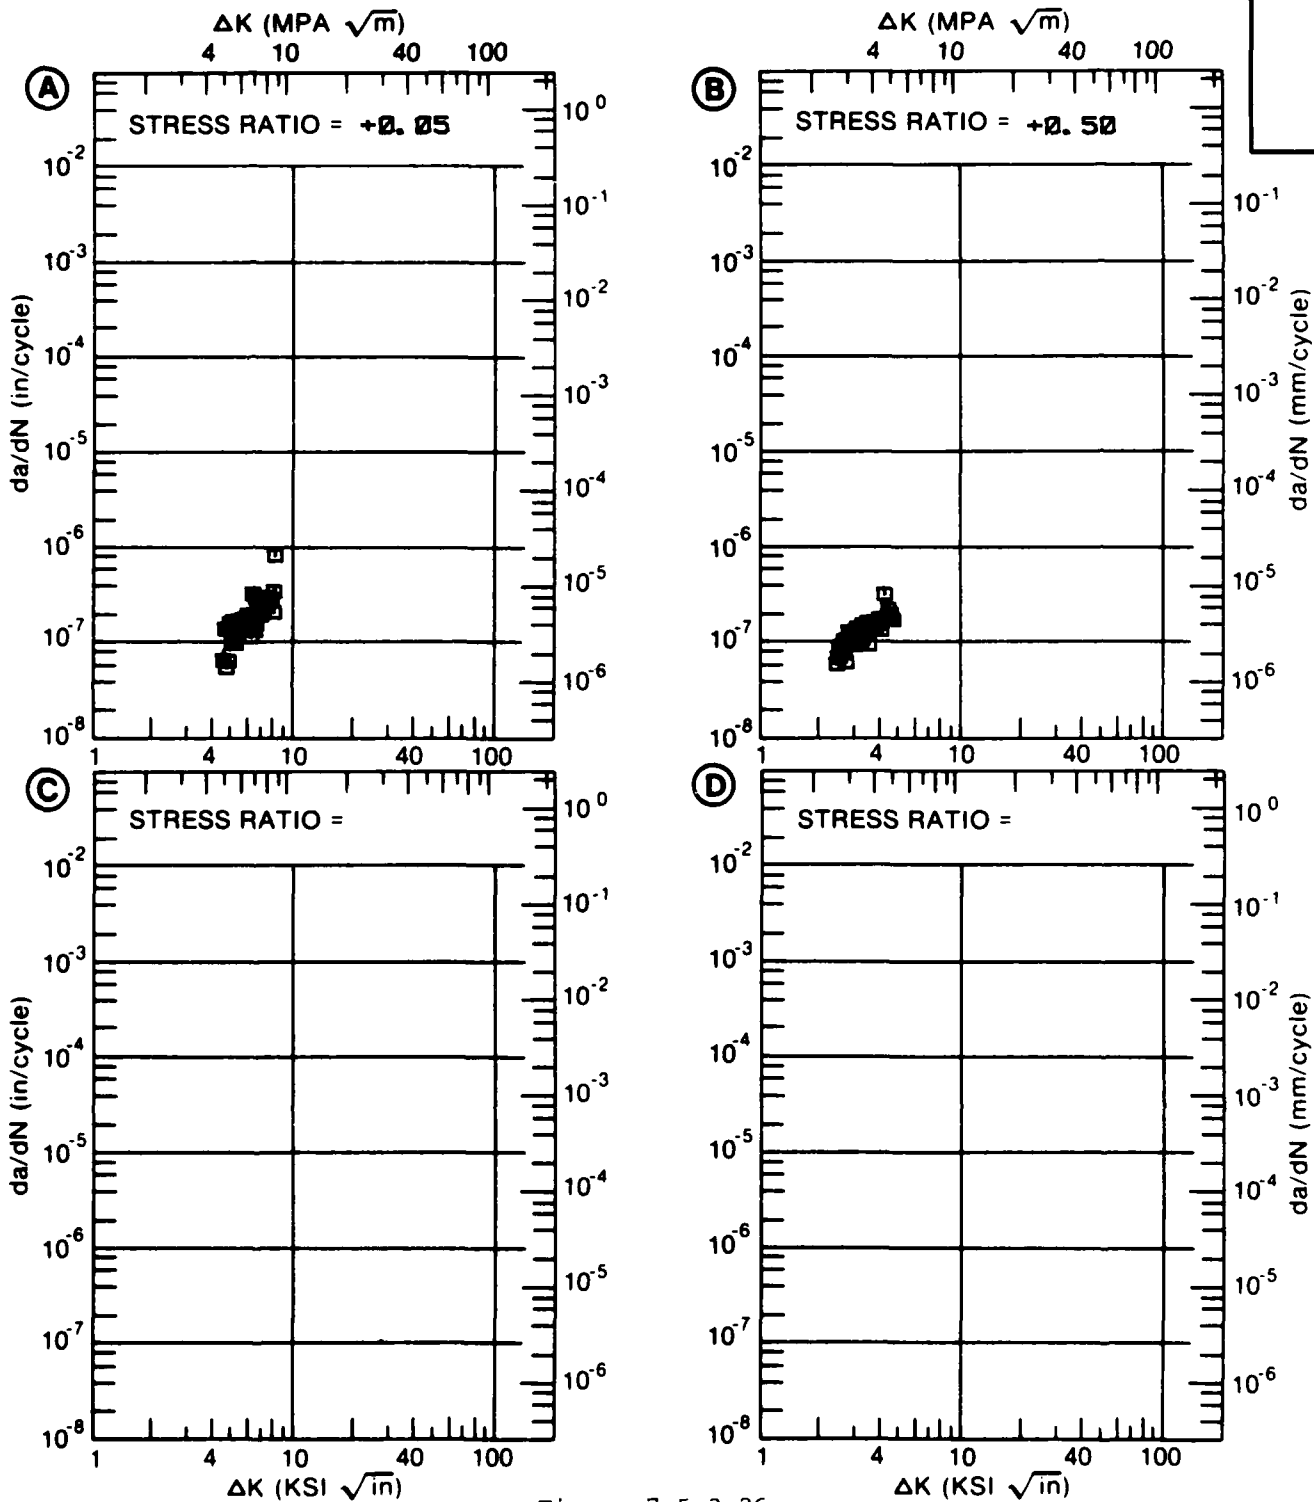


Figure 7.5.3.26

TABLE 7.5.3.27

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.27 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T3511
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.05	R=+0.50		
DELTA K MIN	A: 5.00	.0615			
	B: 2.35		.0342		
	C:				
	D:				
	2.50		.0555		
	3.00		.114		
	3.50		.160		
	4.00		.280		
	5.00	.0615			
	6.00	.141			
	7.00	.514			
	8.00	1.72			
	9.00	4.22			
	10.00	7.05			
DELTA K MAX	A: 10.62	7.90			
	B: 4.18		.380		
	C:				
	D:				

ROOT MEAN SQUARE 33.49 26.13
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T3511
 FORM: EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 9.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 58.7 KSI
 ULT. STRENGTH: 79.3 KSI
 SPECIMEN THK: 0.370"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: BW001

ALUM.
ALLOY

2024

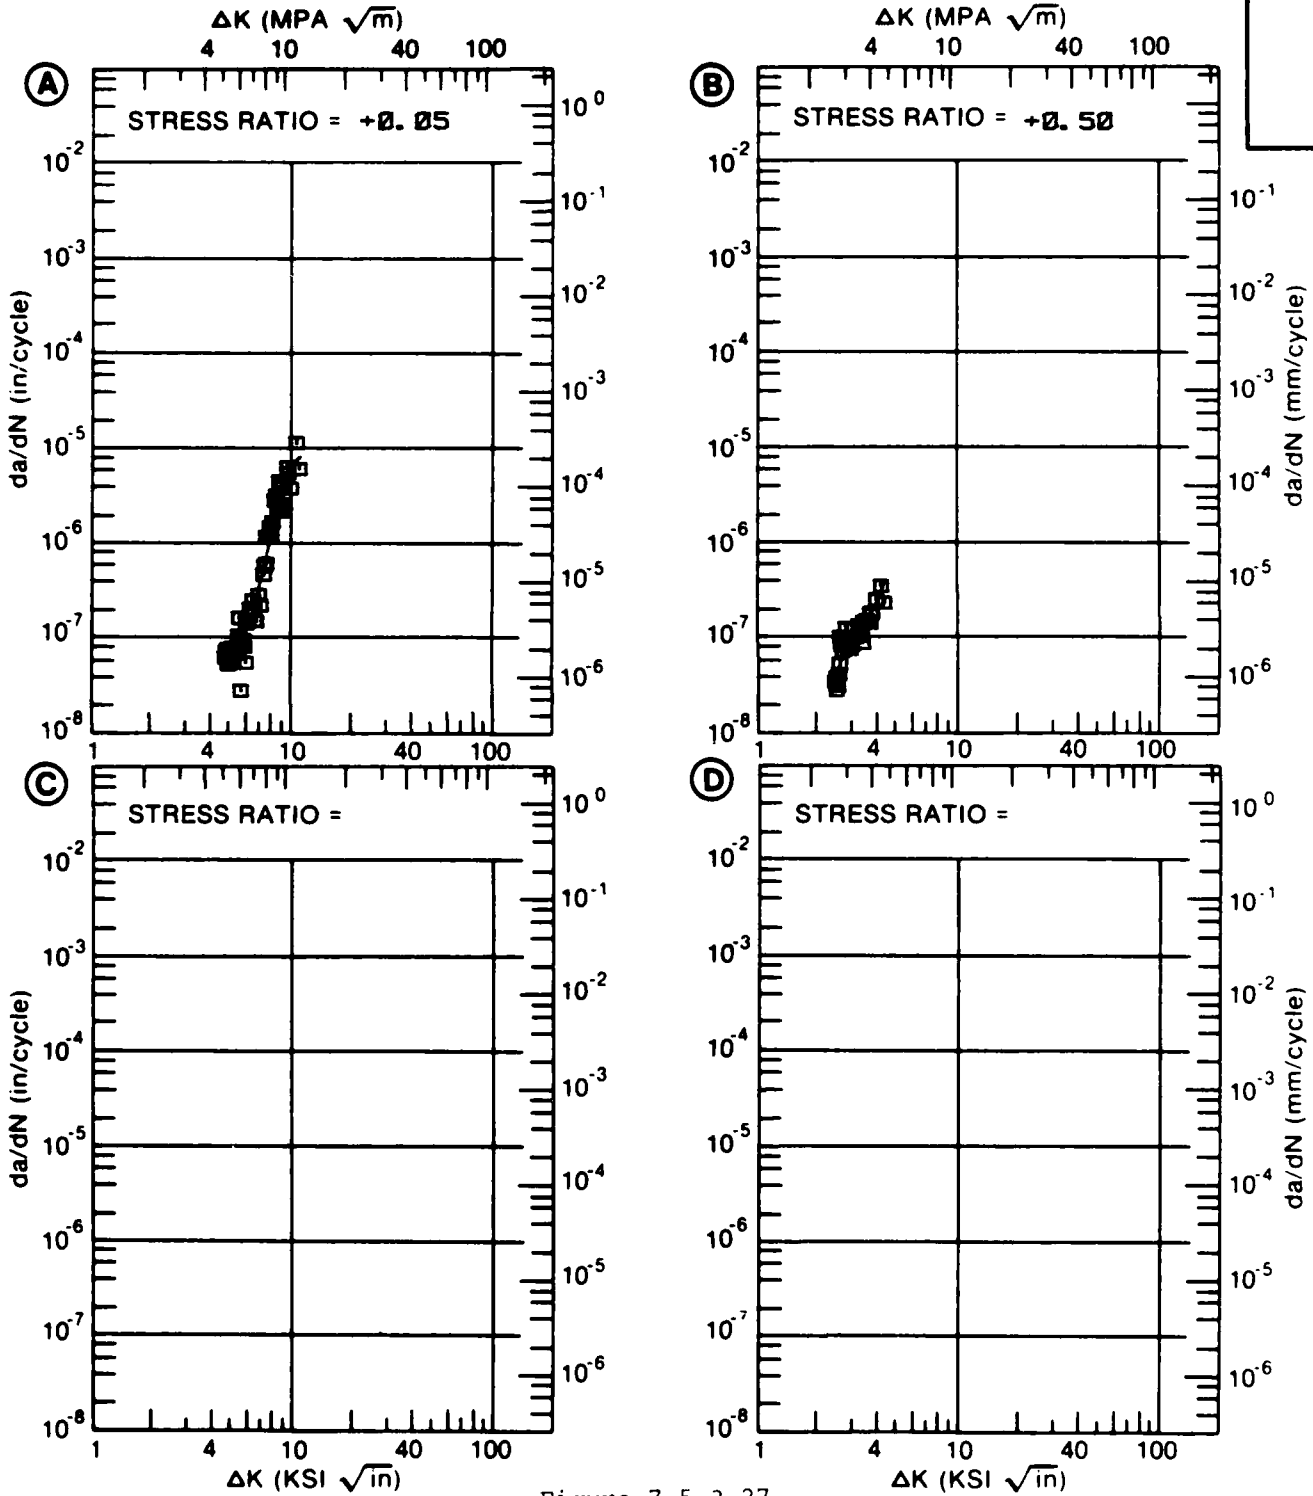


Figure 7.5.3.27

TABLE 7.5.3.28

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.28 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T3511
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.50			
DELTA K	A: 3.57	.169			
MIN	B:				
	C:				
	D:				
	4.00	.164			
	5.00	.431			
	6.00	1.38			
	7.00	3.12			
	8.00	5.19			
	9.00	7.30			
	10.00	9.35			
	13.00	16.2			
	16.00	28.0			
	20.00	62.3			
	25.00	173.			
DELTA K	A: 28.79	239.			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 29.74
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T3511
 FORM: EXTRUSION
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 9.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 58.7 KSI
 ULT. STRENGTH: 79.3 KSI
 SPECIMEN THK: 0.370"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: BW001

ALUM.
ALLOY

2024

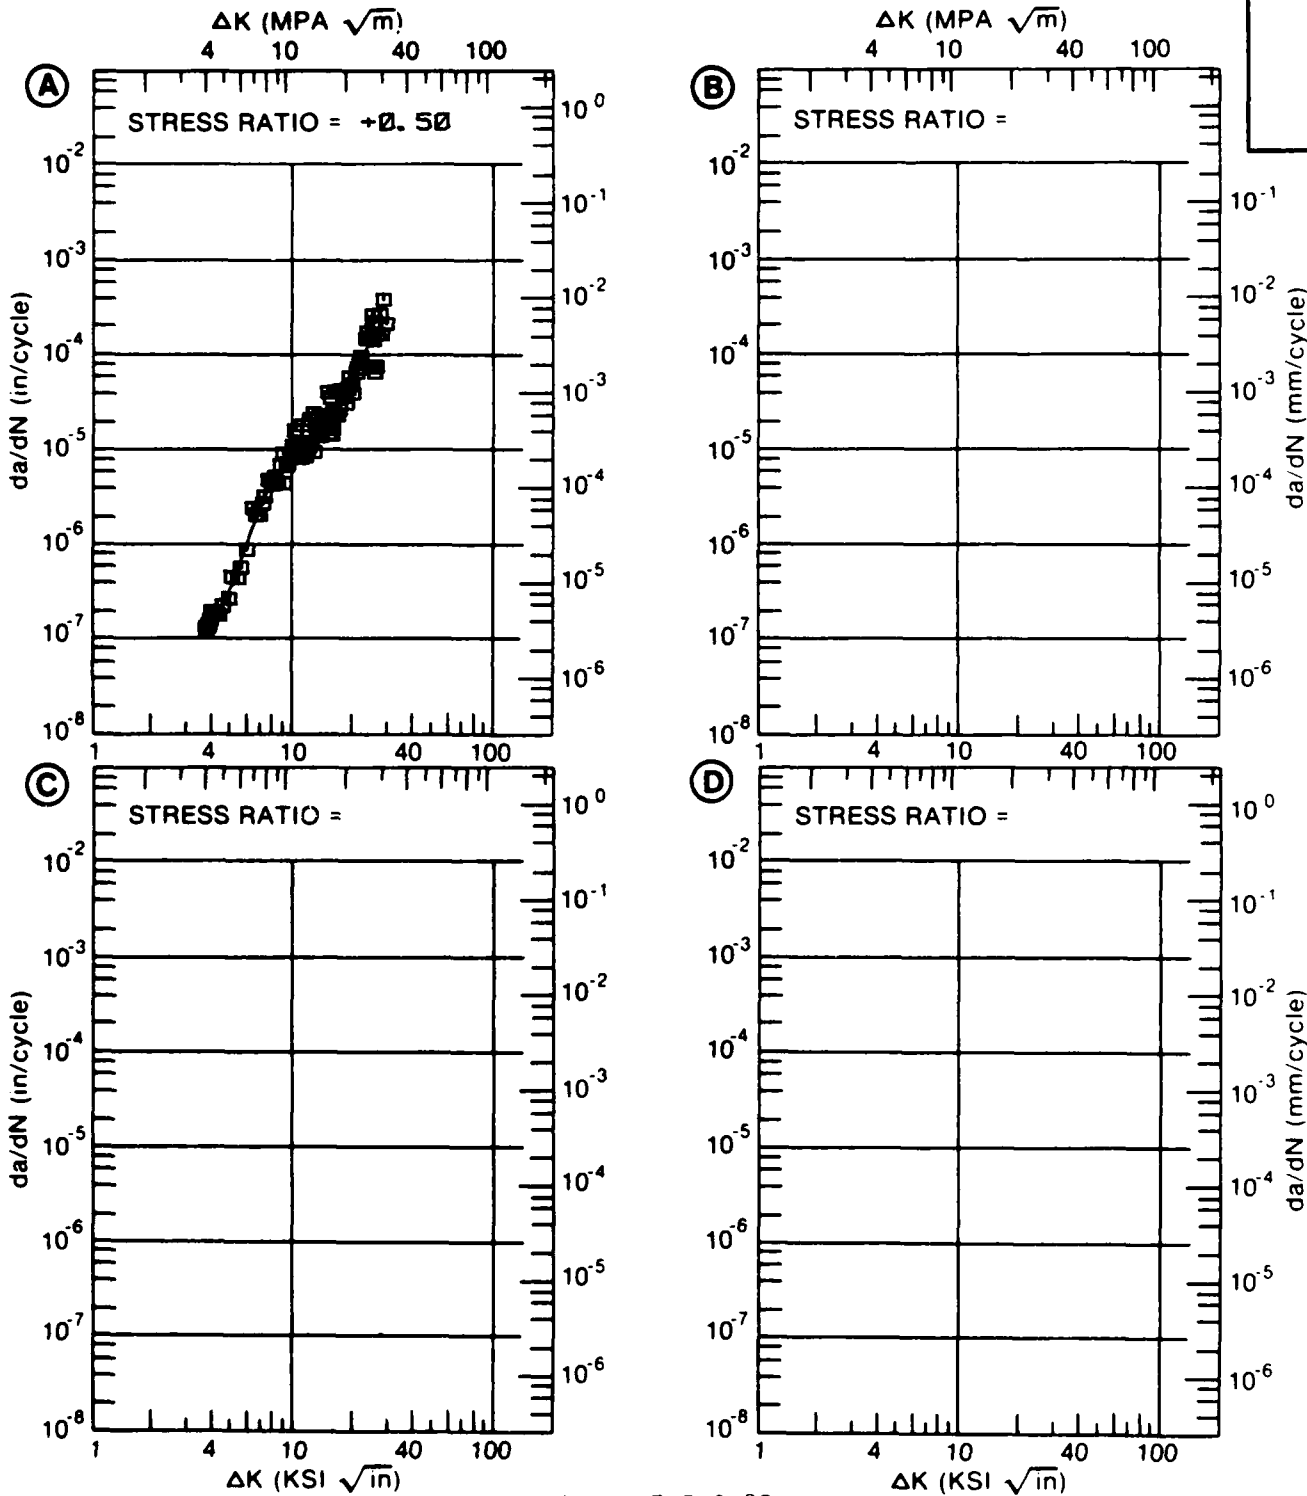


Figure 7.5.3.28

TABLE 7.5.3.29

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.29 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T3511
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10^{-6} IN. /CYCLE)			
	A	B	C	D
	R=-1.00	R=-0.20	R=+0.04	R=+0.40

A:
DELTA K B:
MIN C:
D:
200.00

A:
DELTA K B:
MAX C:
D:

ROOT MEAN SQUARE PERCENT ERROR	A	B	C	D
	0.00	0.00	0.00	0.00

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T3511
 FORM: 0.20" TH EXTRUSION
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 6.0 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 61.2 KSI
 ULT. STRENGTH: 80.4 KSI
 SPECIMEN THK:
 SPECIMEN WIDTH: 4.000"
 REFERENCES: BW005

ALUM.
ALLOY

2024

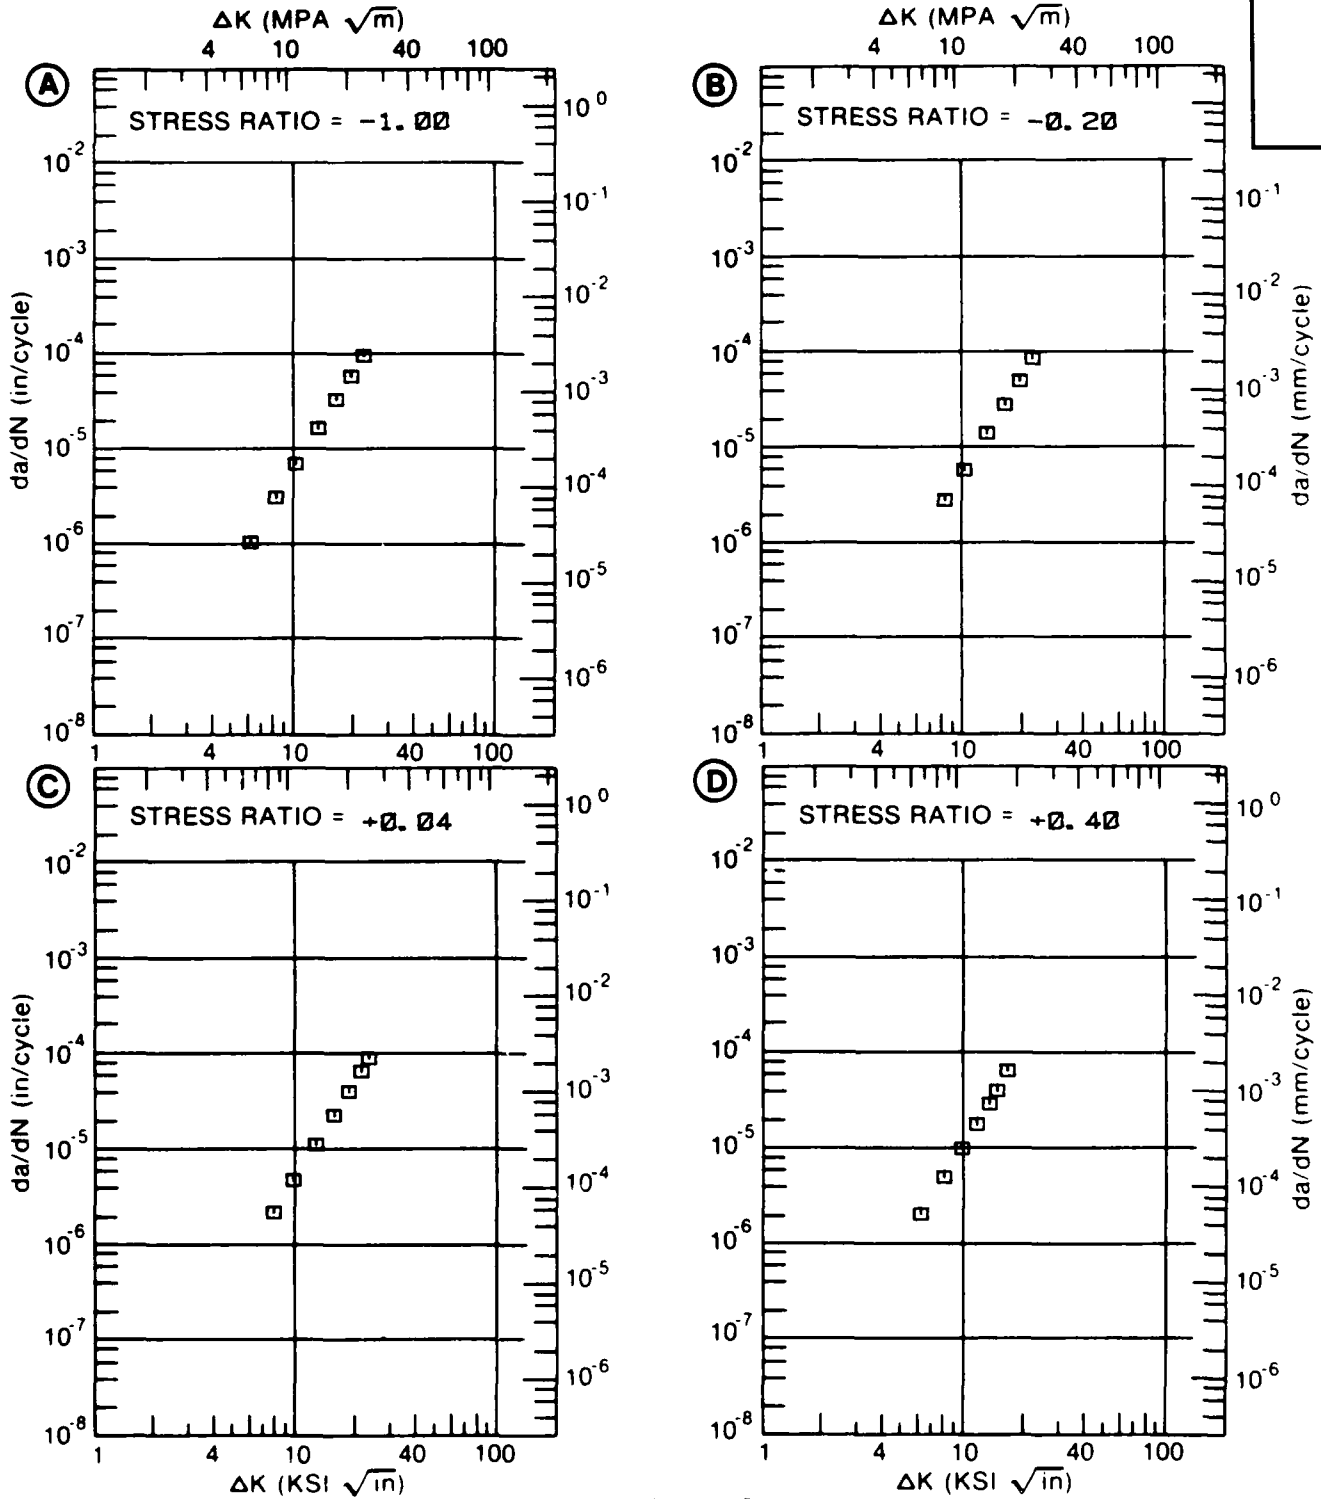


Figure 7.5.3.29

TABLE 7.5.3.30

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.30 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T42					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=-1.00	R=+0.02	R=+0.50	
DELTA K A:	5.48	.651			
DELTA K B:	5.32		.187		
MIN C:	4.18			.187	
D:					
	5.00			.424	
	6.00	1.04	.275	1.20	
	7.00	2.03	.685	2.33	
	8.00	3.29	1.53	3.86	
	9.00	4.76	2.75	5.73	
	10.00	6.41	4.25	7.89	
	13.00	12.7	9.49	15.8	
	16.00	22.2	15.1	25.7	
	20.00	44.3	23.6	42.5	
	25.00	101.	40.0	72.3	
	30.00	223.	70.9	118.	
	35.00	468.	134.	188.	
	40.00	939.	271.		
	50.00	2809.	1131.		
	60.00		3097.		
DELTA K A:	55.92	4173.			
DELTA K B:	67.71		4480.		
MAX C:	39.01			271.	
D:					
ROOT MEAN SQUARE		28.64	47.76	16.10	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T42
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 45.4 KSI
 ULT. STRENGTH: 68.5 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: MA006

ALUM. ALLOY
2024

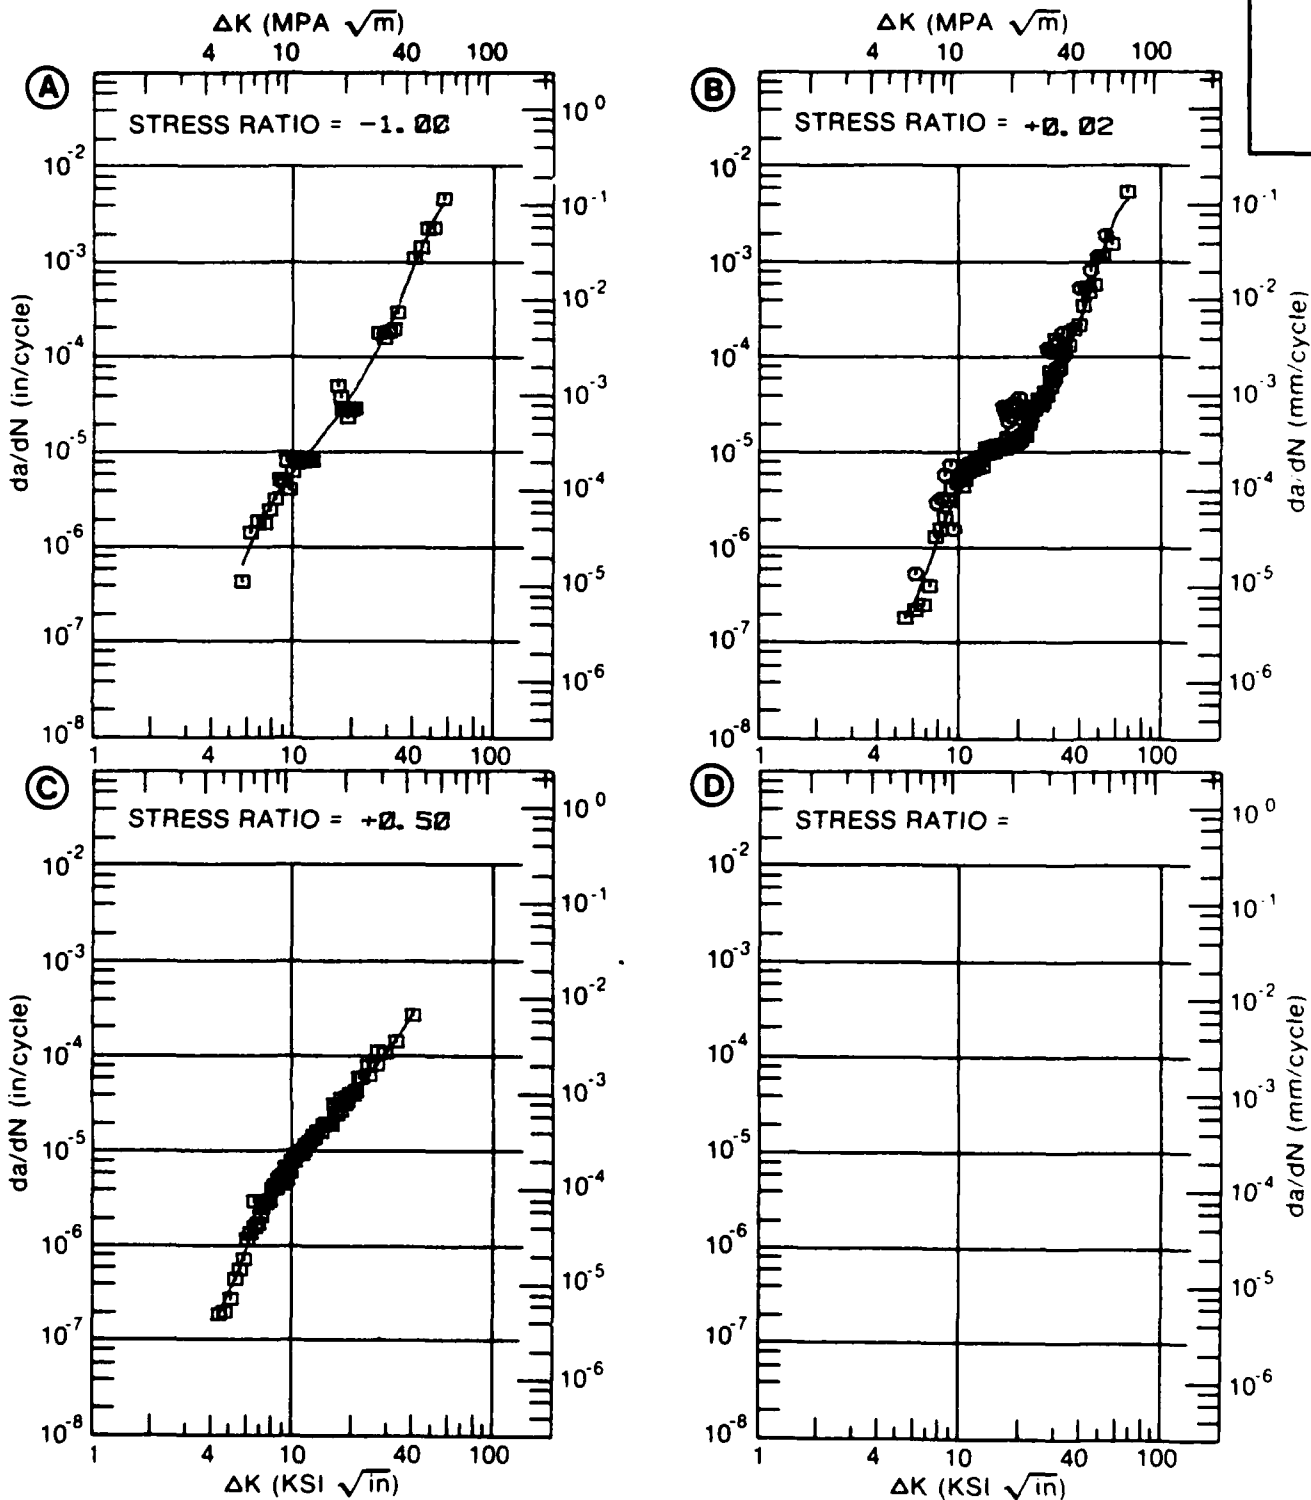


Figure 7.5.3.30

TABLE 7.5.3.31

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.31 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T62
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	R=+0.10	R=+0.30		
DELTA K A: 4.12	.24			
MIN B: 3.95		.08		
C: 1				
D:				
4.00		.0912		
5.00	.312	.465		
6.00	.503	1.32		
7.00	.916	2.74		
8.00	1.74	4.68		
9.00	3.03	7.13		
10.00	4.68	10.1		
13.00	11.8	22.4		
16.00	23.1	42.8		
20.00		96.4		
DELTA K A: 19.00	37.5			
MAX B: 20.04		97.2		
C:				
D:				

ROOT MEAN SQUARE 14.55 35.15
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0 1
(NP/NA) >2.0

CONDITION/HT: T62
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 60.3 KSI
 ULT. STRENGTH: 74.9 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: G0004

ALUM.
 ALLOY
 2024

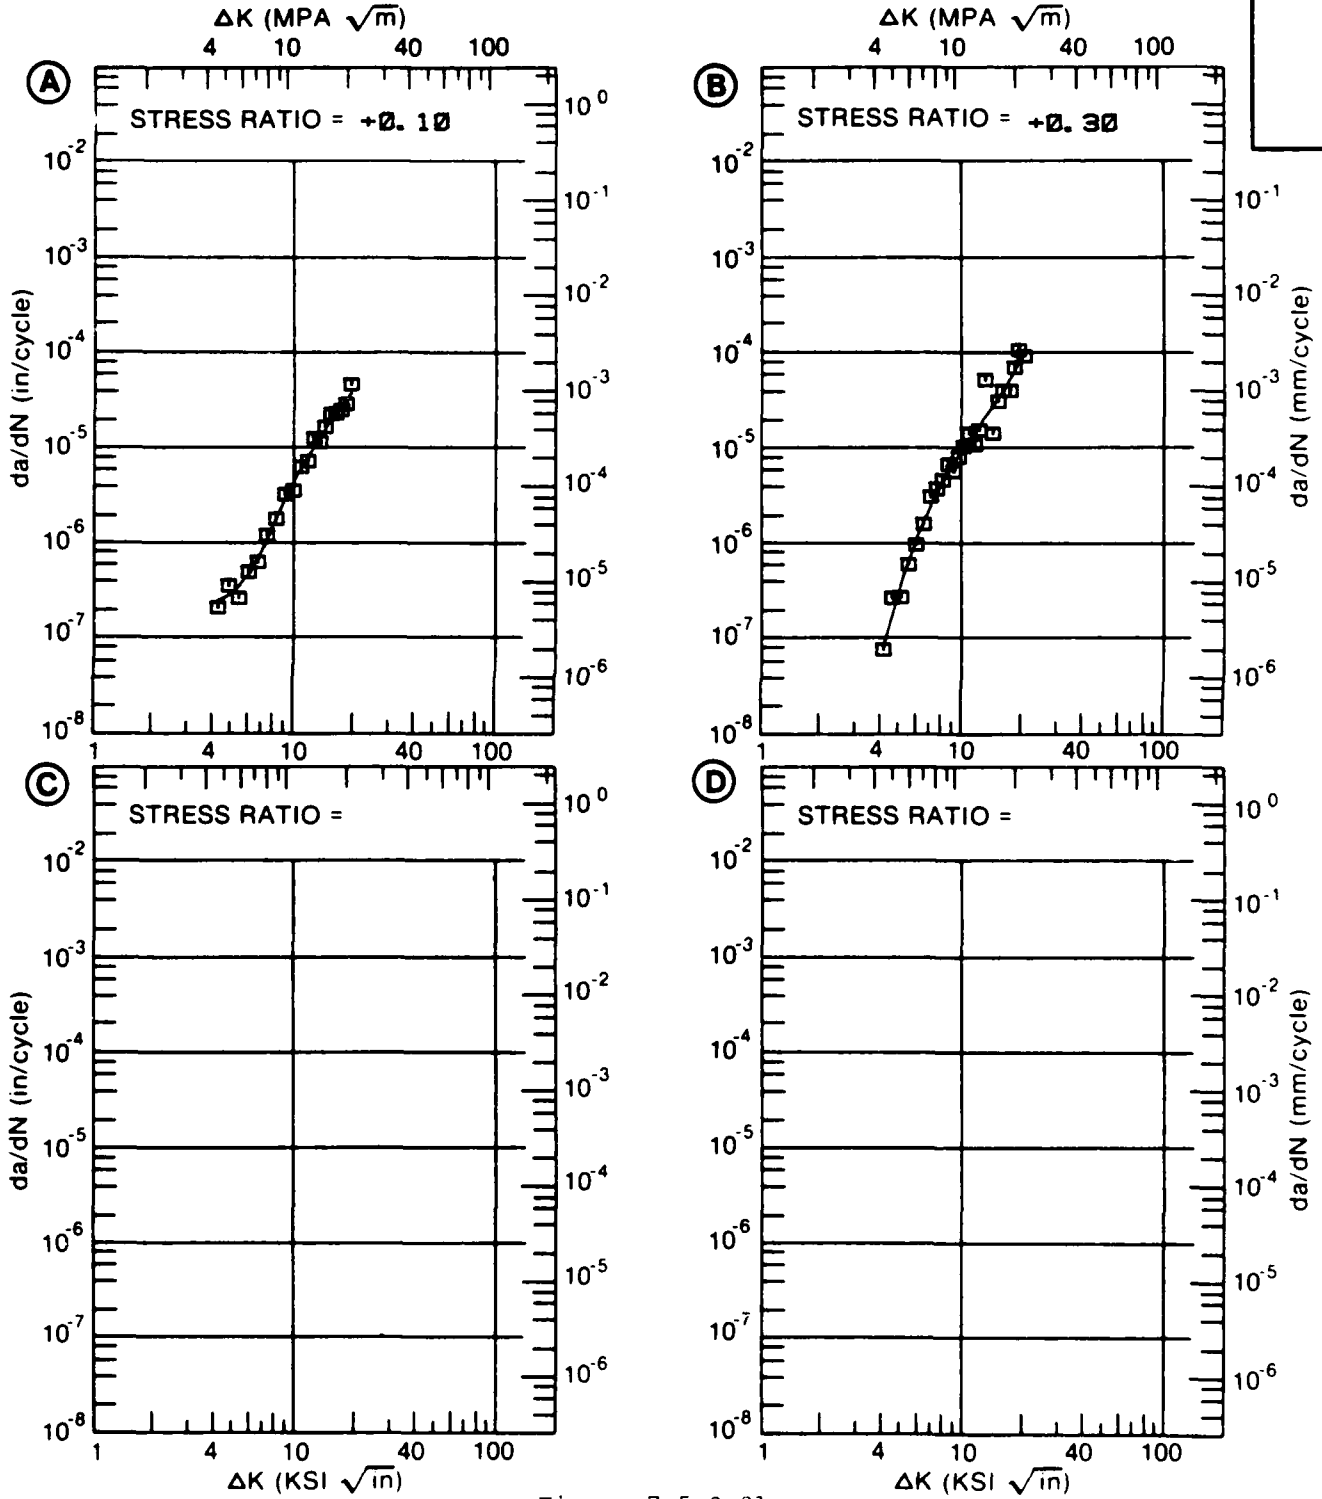


Figure 7.5.3.31

TABLE 7.5.3.32

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.32 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T62					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 50	R=+0. 70	
DELTA K	A: 4. 46	. 336			
MIN	B: 2. 50		. 138		
	C: 2. 69			. 150	
	D:				
	3. 00		. 279	. 268	
	3. 50		. 374	. 413	
	4. 00		. 561	. 716	
	5. 00	. 772	1. 43	2. 05	
	6. 00	1. 73	3. 17	3. 66	
	7. 00	3. 63	5. 53	5. 78	
	8. 00	5. 17	7. 59	10. 7	
	9. 00	6. 29			
	10. 00	7. 61			
	13. 00	20. 8			
	16. 00	53. 1			
DELTA K	A: 19. 67	57. 0			
MAX	B: 8. 83		8. 35		
	C: 8. 21			12. 0	
	D:				
ROOT MEAN SQUARE		17. 67	32. 04	13. 00	
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25			1	
SUMMARY	1. 25-2. 0	1	1		
(NP/NA)	>2. 0				

CONDITION/HT: T62
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 60.3 KSI
 ULT. STRENGTH: 74.9 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
 ALLOY
 2024

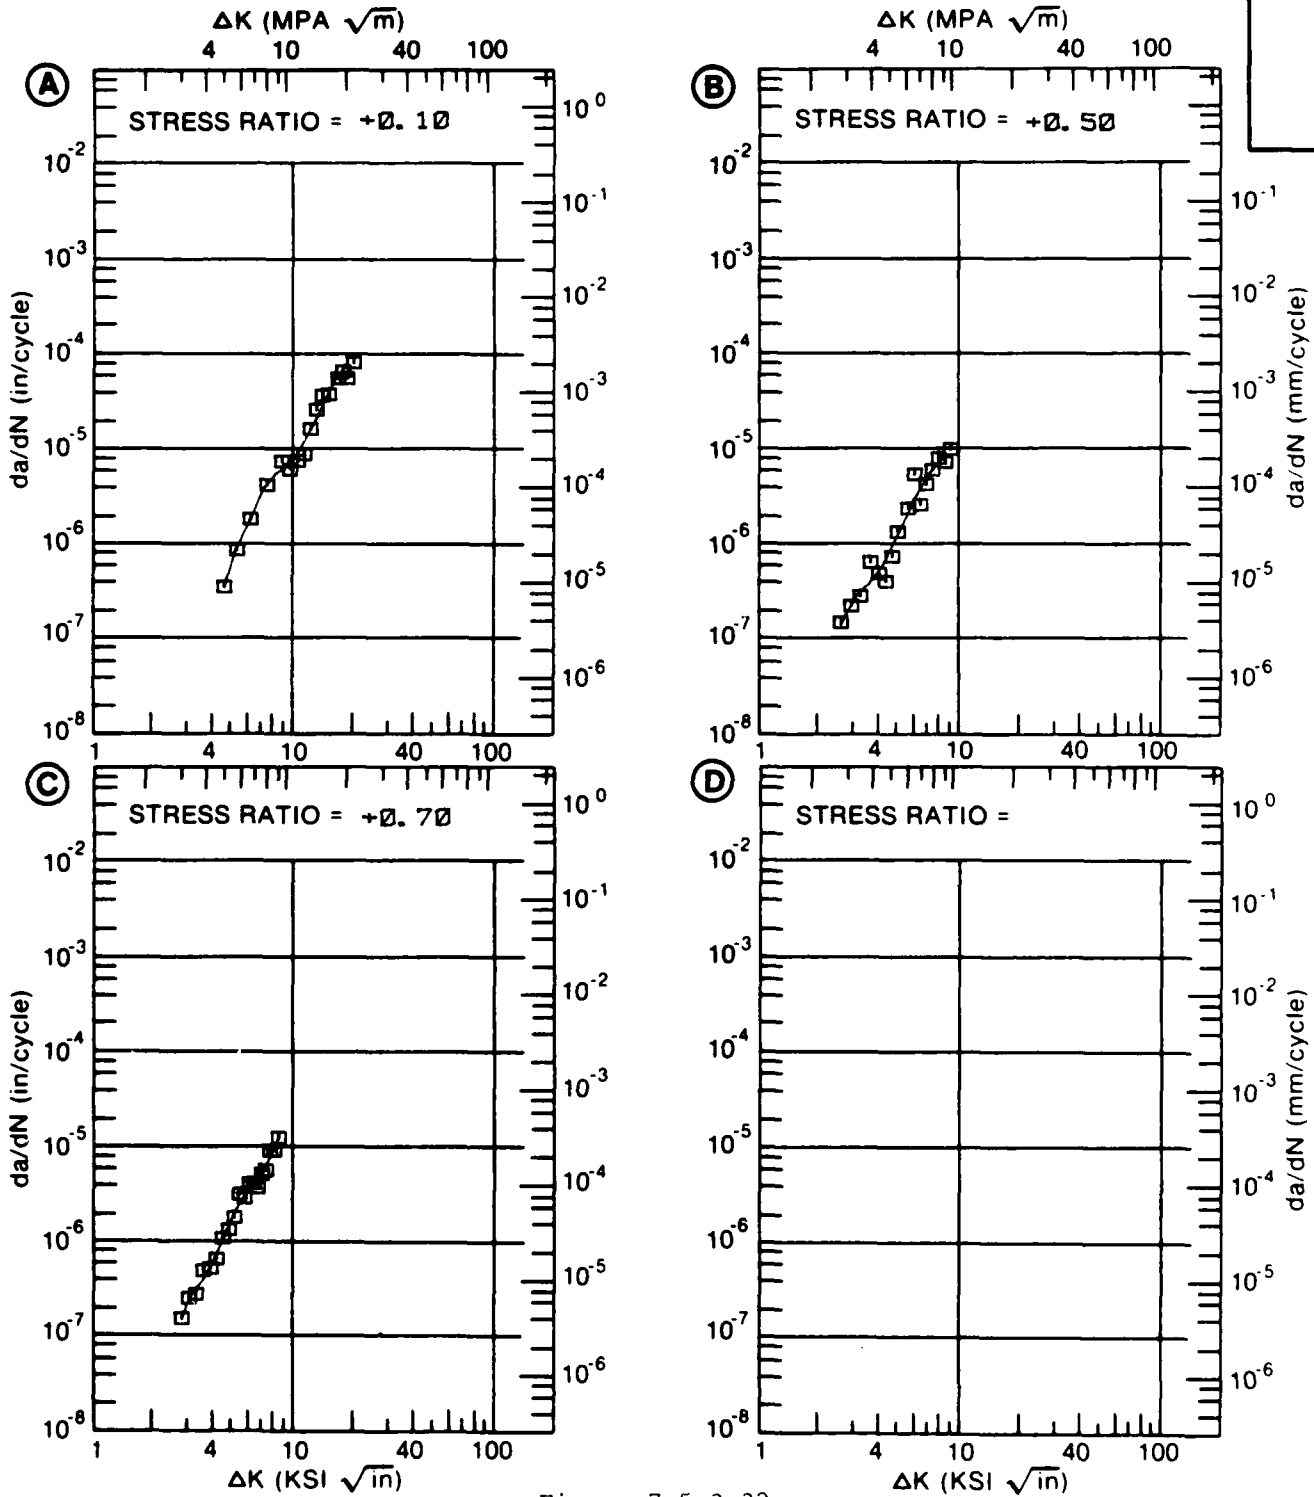


Figure 7.5.3.32

TABLE 7.5.3.33

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.33 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T62
ENVIRONMENT: R. T. , DRY AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 30	R=+0. 50	
DELTA K MIN	A: 4. 17	. 299			
	B: 3. 56		. 129		
	C: 2. 36			. 0347	
	D:				
	2. 50			. 0456	
	3. 00			. 105	
	3. 50			. 206	
	4. 00		. 190	. 366	
	5. 00	. 812	. 711	. 947	
	6. 00	1. 89	1. 86	2. 07	
	7. 00	3. 47	3. 54	4. 08	
	8. 00	5. 56	5. 68	7. 43	
	9. 00	8. 15	8. 24	10. 6	
	10. 00	11. 3	11. 3	13. 1	
	13. 00	24. 6	25. 8		
	16. 00	46. 7	58. 9		
DELTA K MAX	A: 16. 21	48. 7			
	B: 19. 40		125.		
	C: 12. 69			29. 0	
	D:				

ROOT MEAN SQUARE 10. 91 11. 42 22. 01
PERCENT ERROR

LIFE PREDICTION RATIO SUMMARY (NP/NA)

0. 0-0. 5			
0. 5-0. 8			
0. 8-1. 25			
1. 25-2. 0	1	1	1
>2. 0			

CONDITION/HT: T62
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 58.2 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
ALLOY

2024

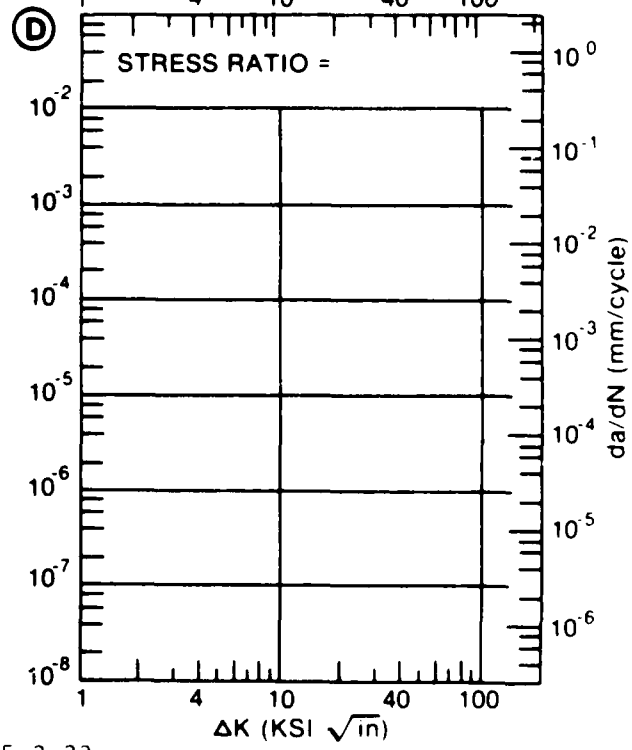
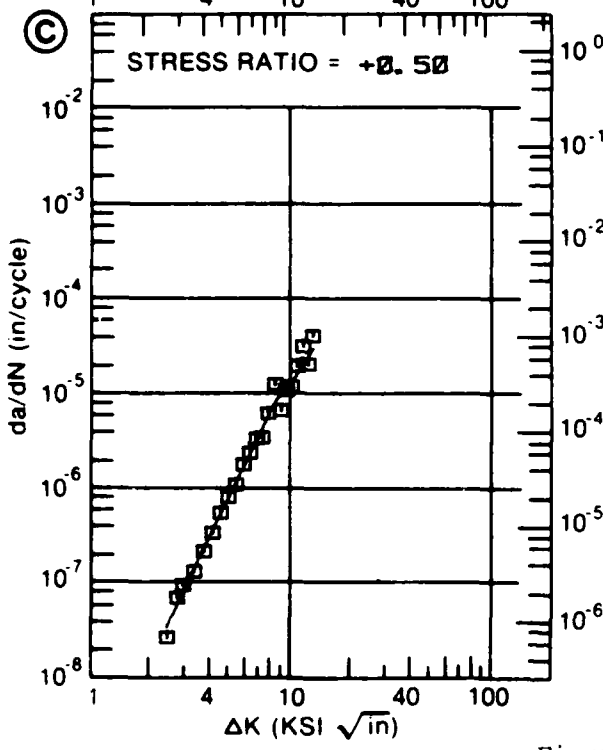
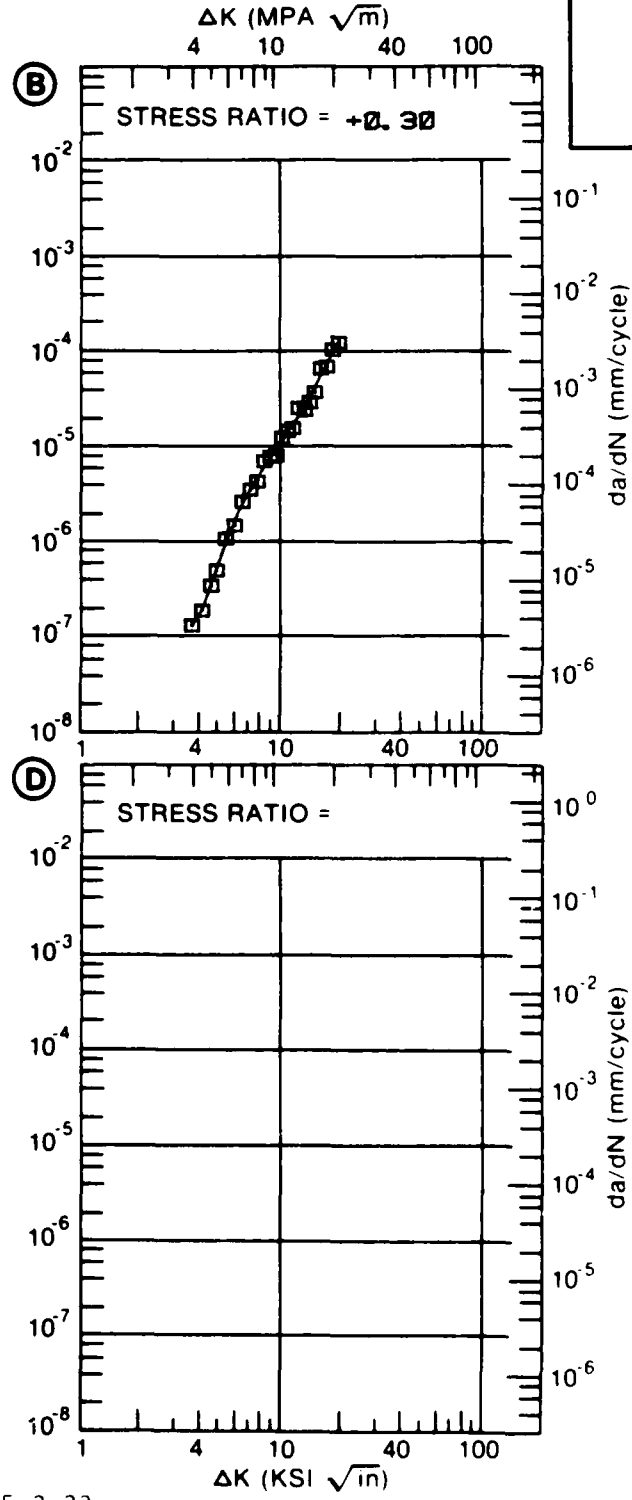
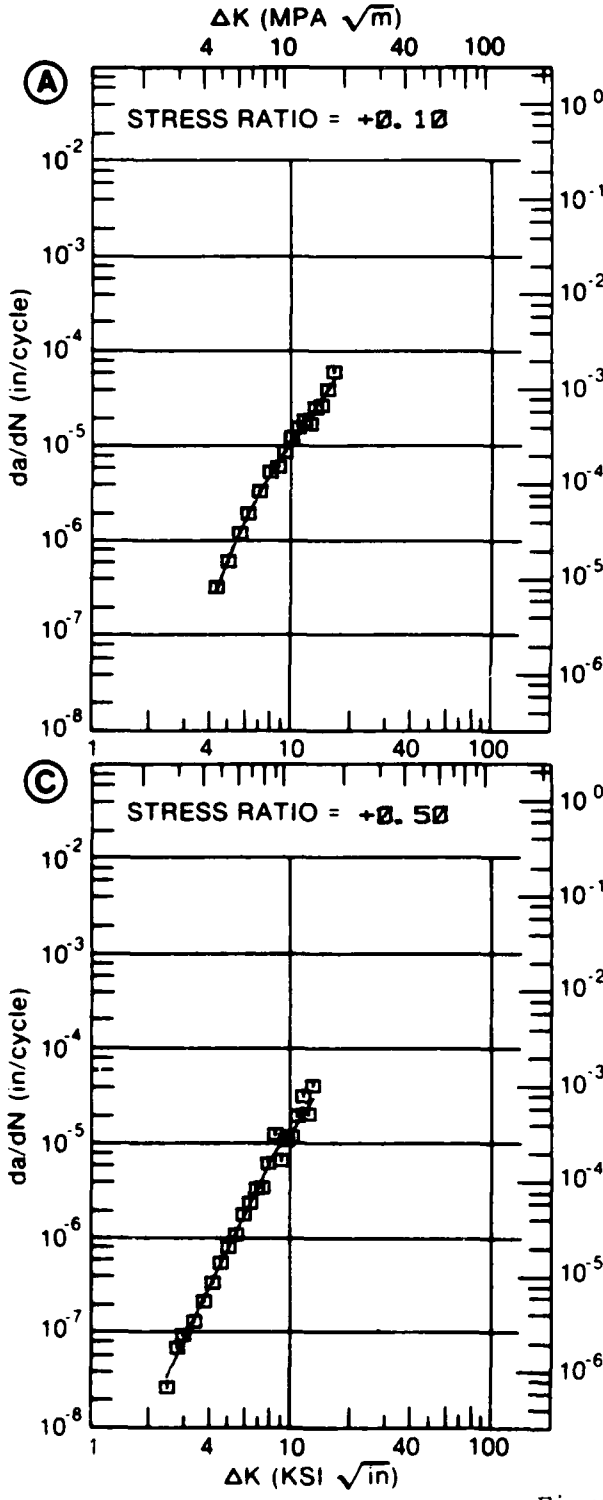


Figure 7.5.3.33

TABLE 7.5.3.34

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.34 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T62					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 30	R=+0. 50	
DELTA K A:					
MIN B:	4. 77		. 573		
C:	2. 25			. 118	
D:					
	2. 50			. 126	
	3. 00			. 178	
	3. 50			. 289	
	4. 00			. 484	
	5. 00		. 787	1. 26	
	6. 00		2. 12	2. 70	
	7. 00		3. 94	4. 70	
	8. 00		6. 07	6. 84	
	9. 00		8. 59	9. 52	
	10. 00		11. 7	14. 5	
	13. 00		29. 9	48. 5	
DELTA K A:					
MAX B:	13. 80		39. 3		
C:	14. 13			56. 2	
D:					
ROOT MEAN SQUARE		0. 00	28. 43	19. 50	
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25			1	
SUMMARY	1. 25-2. 0		1		
(NP/NA)	>2. 0				

CONDITION/HT: T62
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 58.2 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES GD004

ALUM. ALLOY
2024

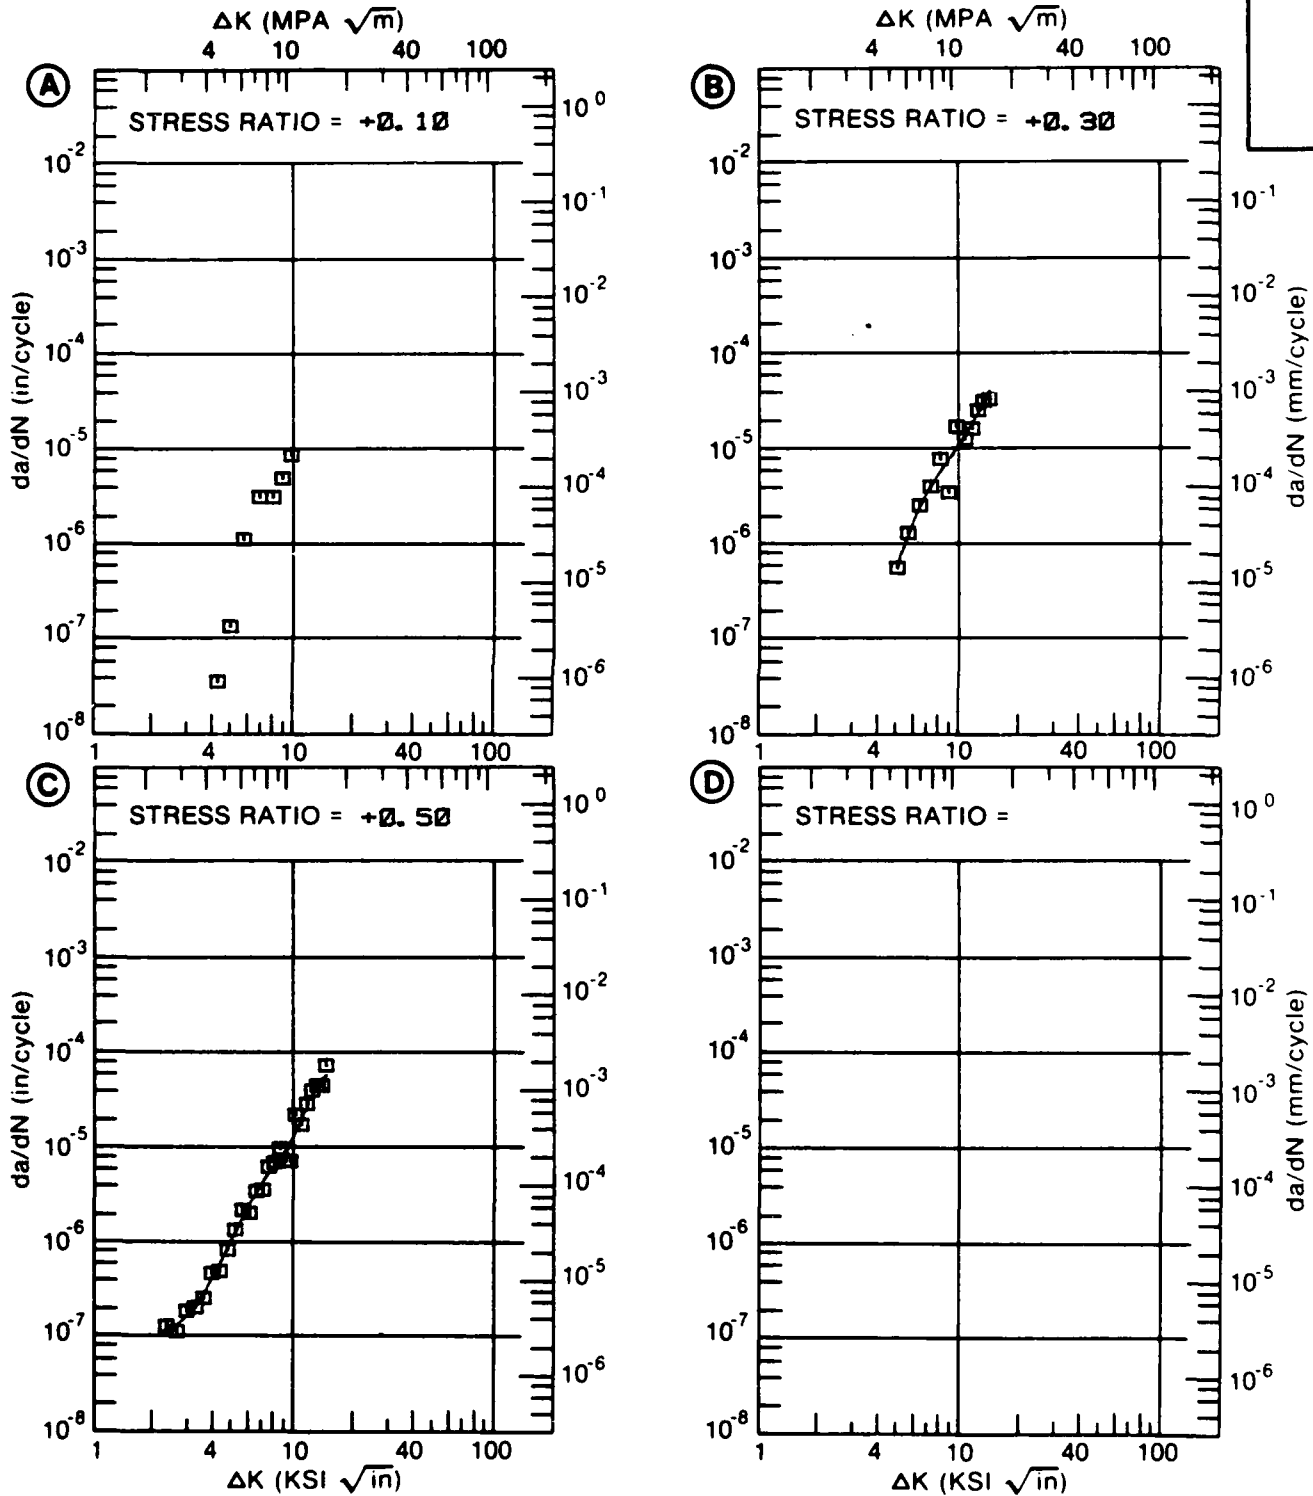


Figure 5.7.3.34

TABLE 7.5.3.35

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.35 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T62					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=-0.25	R=+0.10	R=+0.30	R=+0.50
DELTA K	A: 5.00	.862			
MIN	B: 4.32		.573		
	C: 3.26			.385	
	D: 2.24				.0837
	2.50				.151
	3.00				.166
	3.50			.482	.294
	4.00			.665	.721
	5.00	.862	.696	1.24	2.83
	6.00	1.87	2.08	2.55	4.58
	7.00	3.43	3.91	4.96	6.03
	8.00	3.48	4.86	8.66	9.09
	9.00	3.55	5.26	13.1	15.6
	10.00	4.87	5.87	17.0	25.7
	13.00	23.6	17.0	29.2	
	16.00			92.6	
DELTA K	A: 15.39	43.8			
MAX	B: 15.29		22.2		
	C: 16.37			114.	
	D: 11.22				39.8
ROOT MEAN SQUARE		13.05	11.67	23.59	19.16
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0	1	1	1	1
(NP/NA)	>2.0				

CONDITION/HT: T62
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 58.2 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES GD004

ALUM.
ALLOY

2024

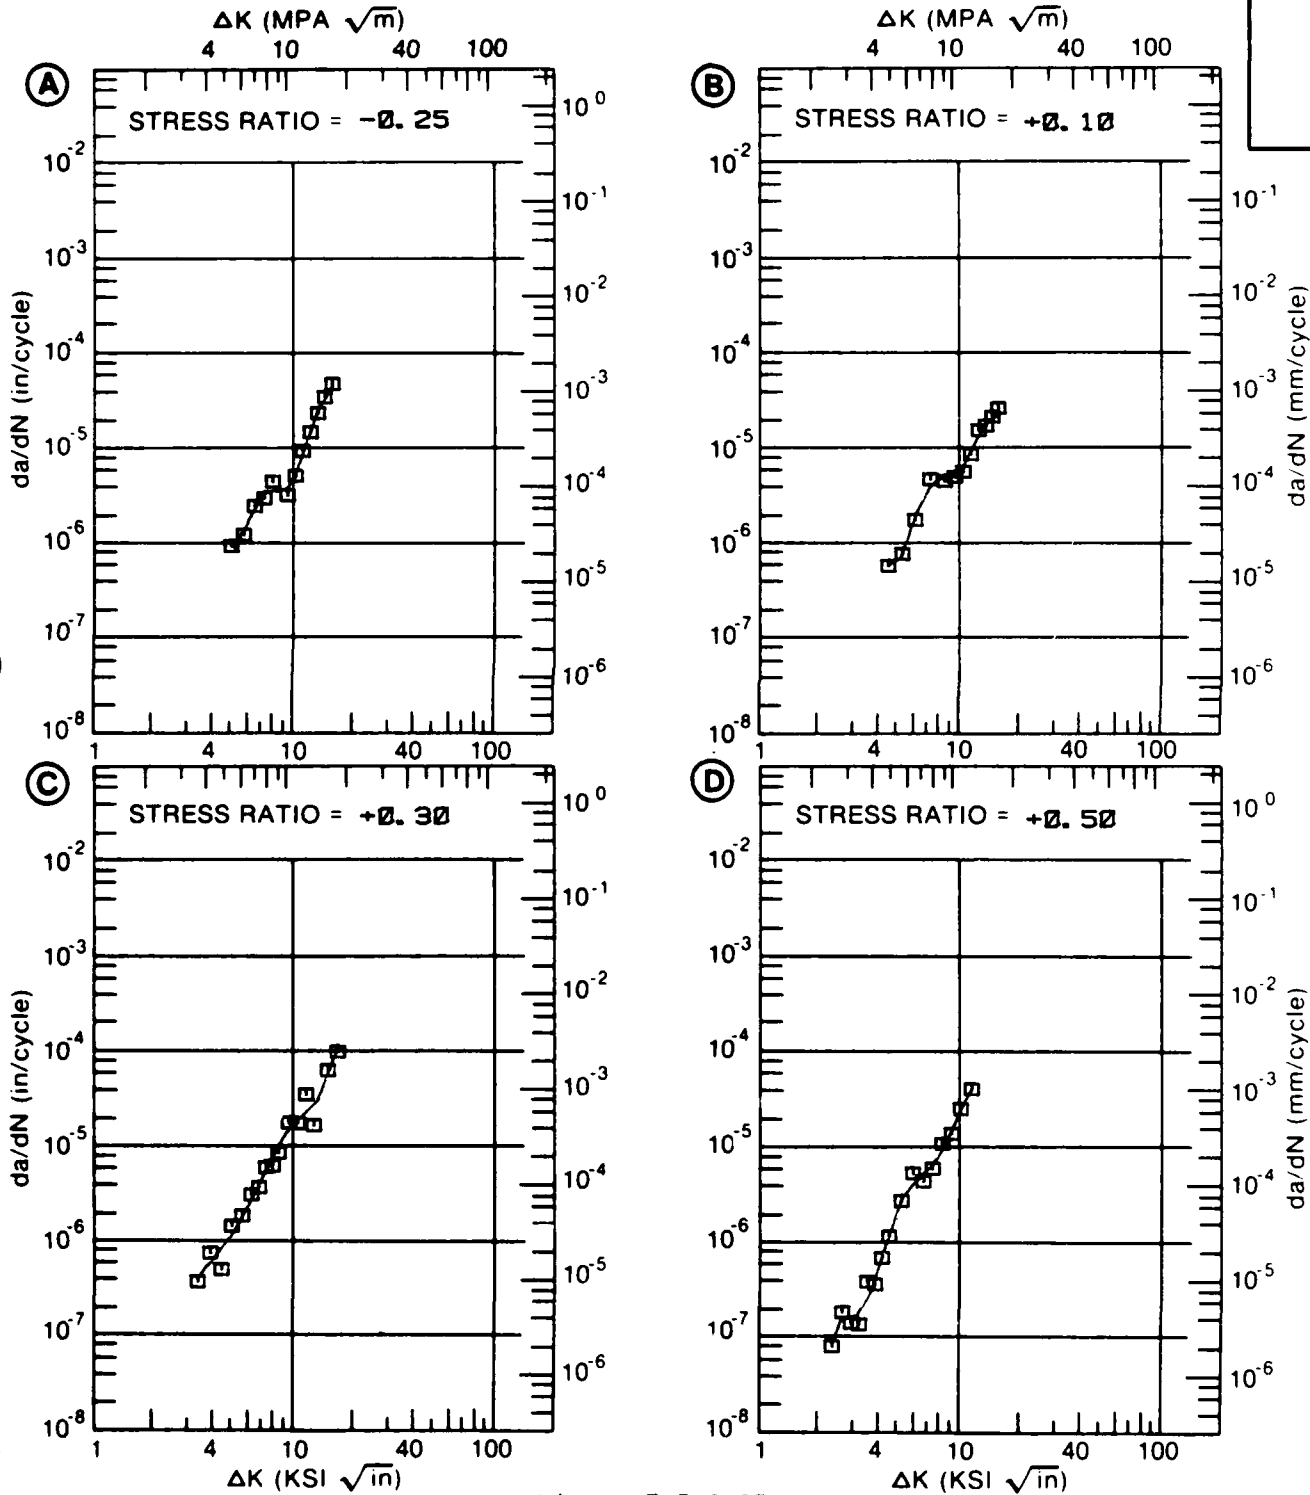


Figure 7.5.3.35

TABLE 7.5.3.36

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.36 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T81
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.05			
DELTA K MIN	A: 10.00	8.08			
	B:				
	C:				
	D:				
	13.00	13.3			
	16.00	26.8			
	20.00	68.1			
	25.00	183.			
	30.00	392.			
	35.00	684.			
DELTA K MAX	A: 36.74	795.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 16.24
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 4
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T81
 FORM: 0.03- 0.04" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 2.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 64.4 KSI
 ULT. STRENGTH: 70.5 KSI
 SPECIMEN THK: 0.032- 0.040"
 SPECIMEN WIDTH: 6.000- 9.700"
 REFERENCES: 86734

ALUM. ALLOY
2024

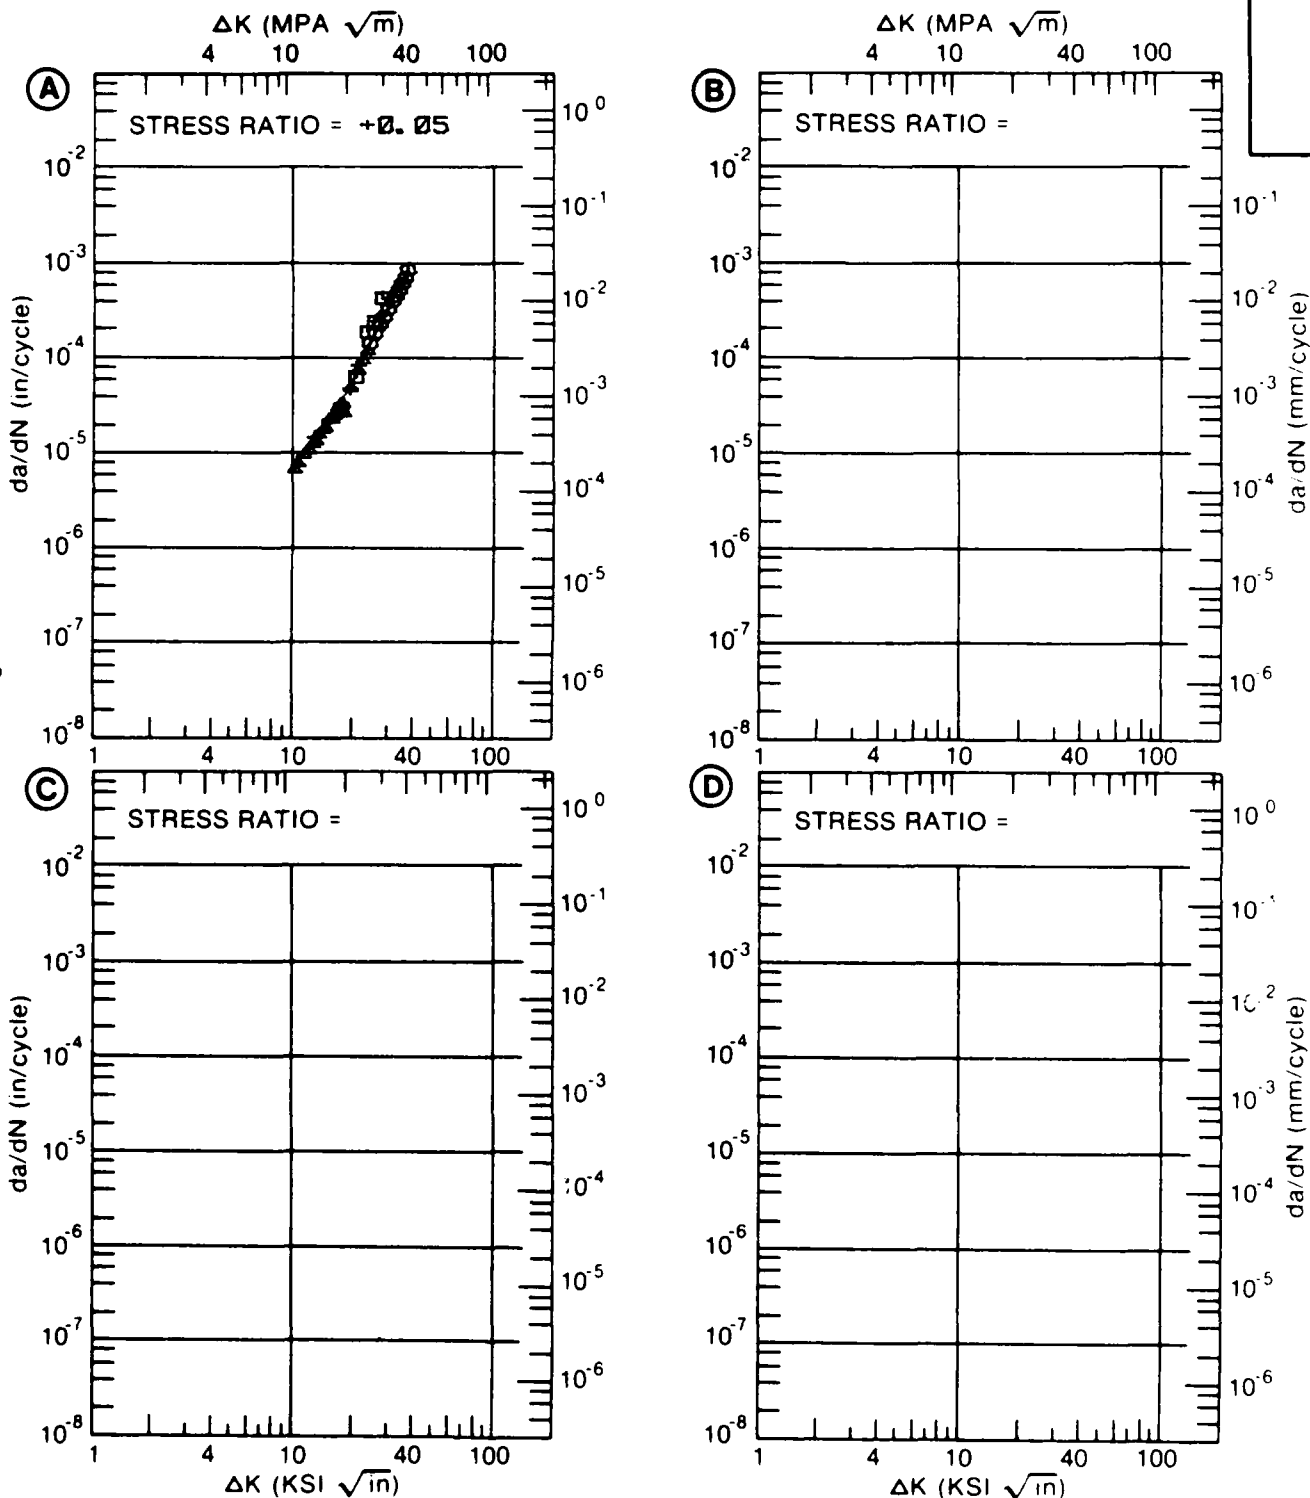


Figure 7.5.3.36

TABLE 7.5.3.37

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.37 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 10.39	12.0			
MIN	B: 13.00	28.7			
	C: 16.00	58.8			
	D: 20.00	106.			
DELTA K	A: 21.09	117.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		3.94			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T81
 FORM: 0.07" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.40
 FREQUENCY: 2.00 HZ

YIELD STRENGTH: 64.4 KSI
 ULT. STRENGTH: 70.5 KSI
 SPECIMEN THK: 0.065"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 86734

ALUM.
ALLOY

2024

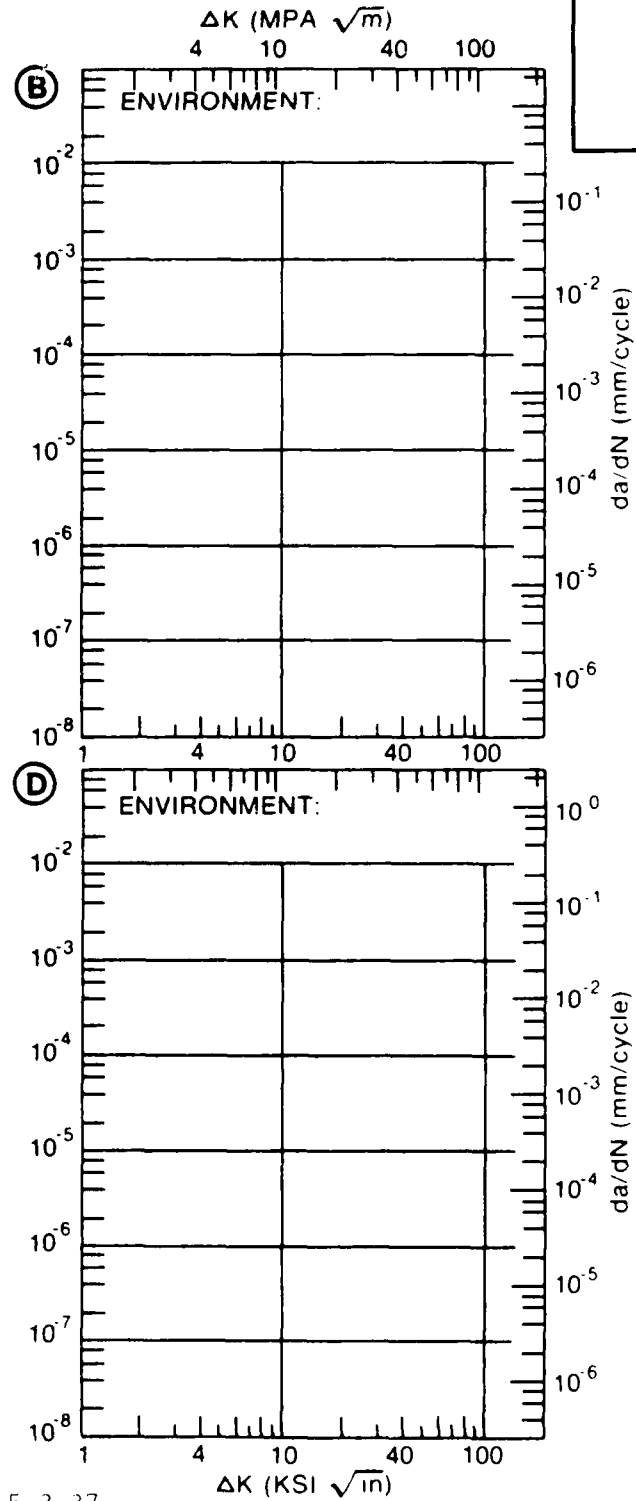
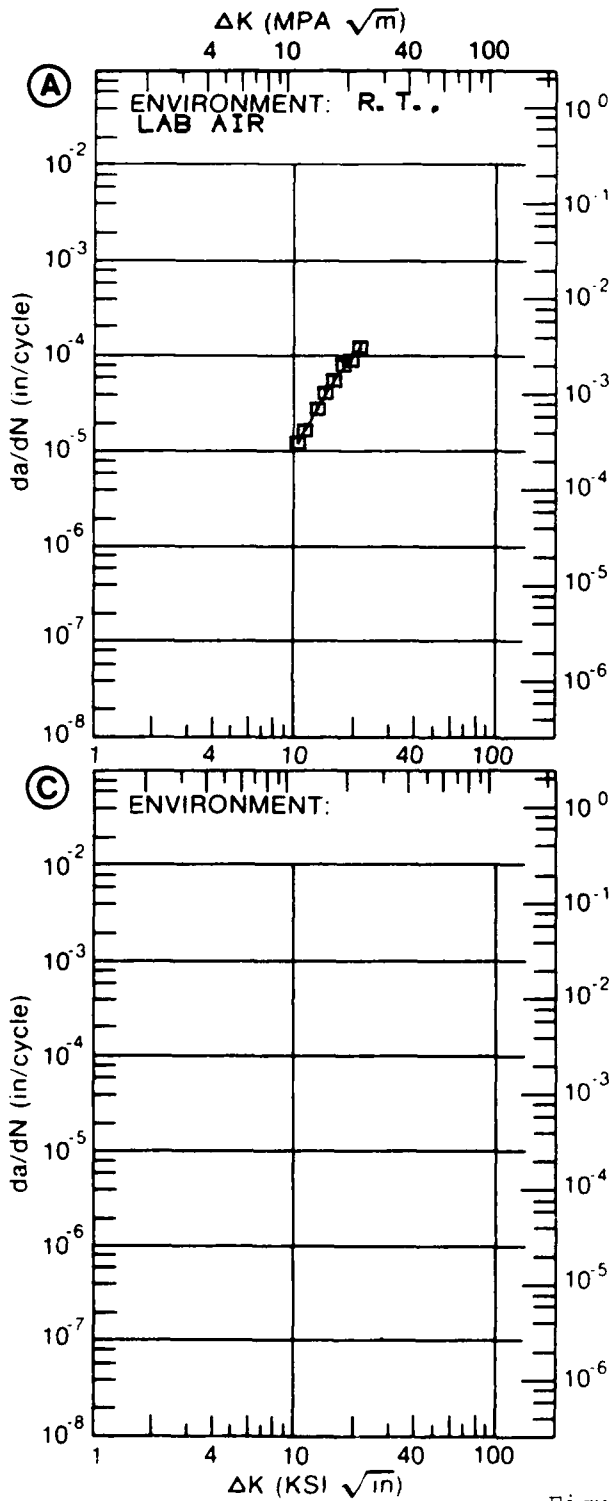


Figure 7.5.3.37

TABLE 7.5.3.38

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.38 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	
DELTA K	A: 5.82	1.16			
MIN	B: 6.20		1.81		
	C: 3.21			.125	
	D:				
	3.50			.299	
	4.00			.533	
	5.00			1.26	
	6.00	1.28		2.46	
	7.00	1.98	3.00	4.31	
	8.00	2.77	4.67	7.11	
	9.00	3.68	6.51	11.3	
	10.00	4.78	8.64	17.6	
	13.00	10.3	19.9	61.3	
	16.00	23.4	54.3	202.	
	20.00	71.8	193.	686.	
	25.00	261.	355.		
	30.00	802.			
DELTA K	A: 32.00	1197.			
MAX	B: 25.06		355.		
	C: 22.07			2750.	
	D:				
ROOT MEAN SQUARE		11.07	21.88	19.67	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25		2	1	
SUMMARY	1.25-2.0	2		1	
(NP/NA)	>2.0				

CONDITION/HT: T81
 FORM: 0.10" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T. . L. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.097- 0.101"
 SPECIMEN WIDTH: 23.660- 23.820"
 REFERENCES: 86575

ALUM.
ALLOY

2024

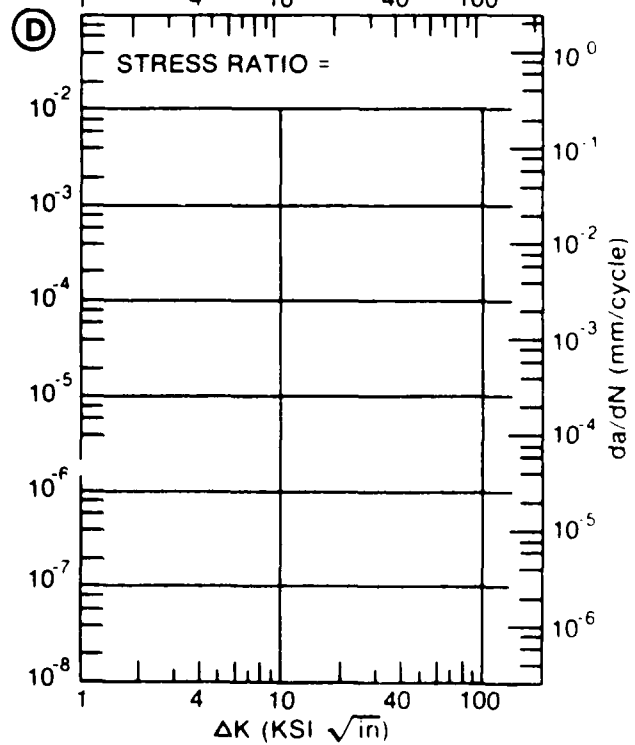
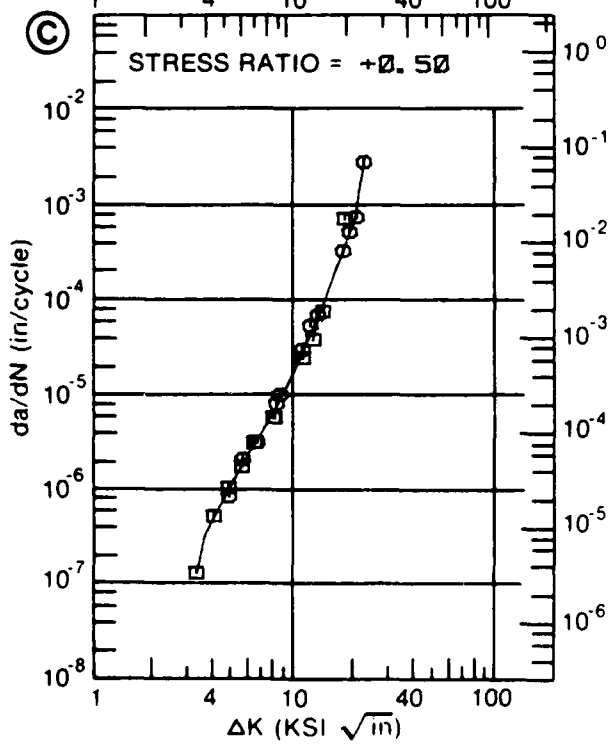
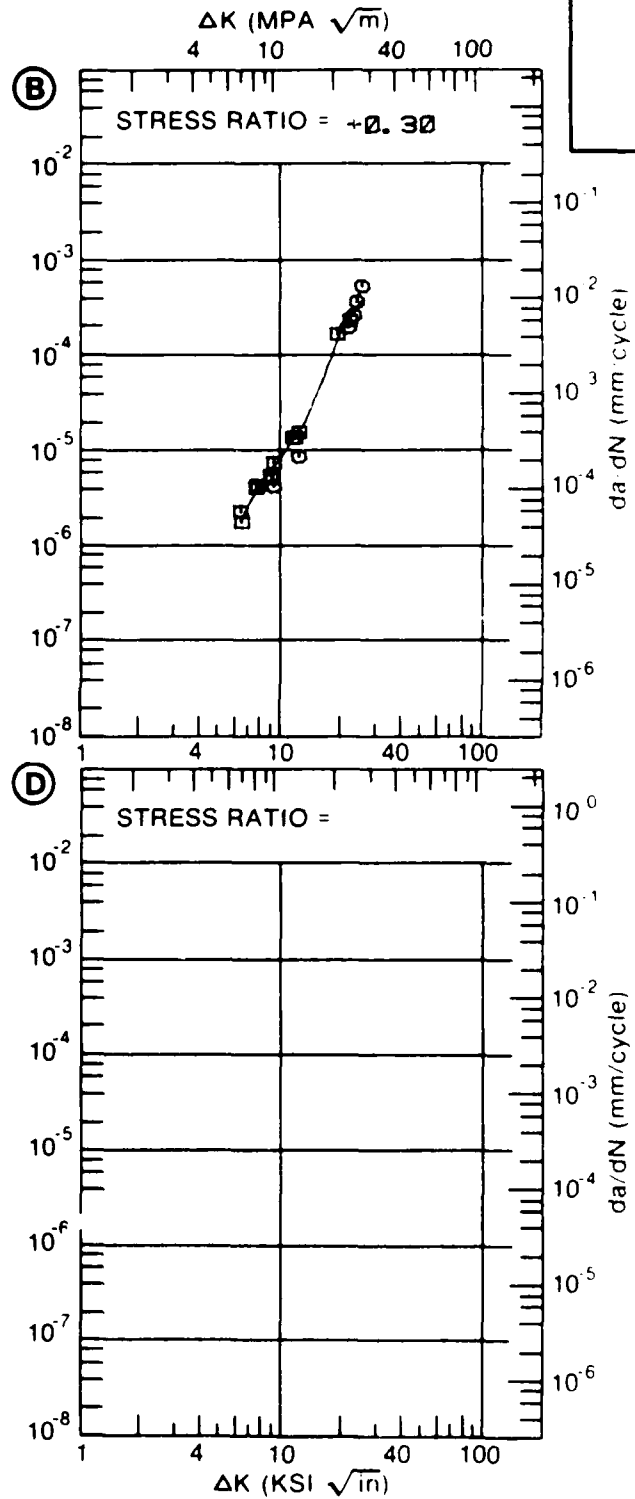
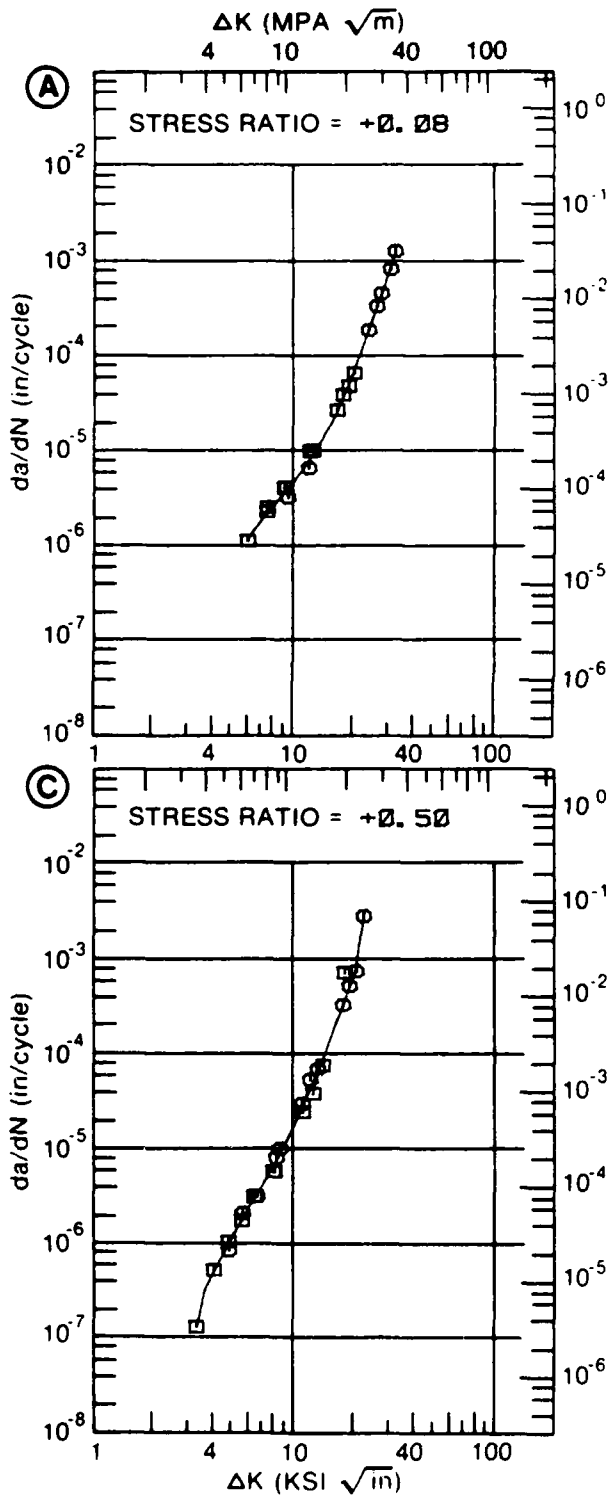


Figure 7.5.3.38

TABLE 7.5.3.39

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.39 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. J. P. 4	E= R. T. S. T. W.	
DELTA K MIN	A: 6.04	.769			
	B: 6.04		1.42		
	C: 6.24			1.87	
	D:				
	7.00	1.71	2.47	2.68	
	8.00	2.93	3.85	4.04	
	9.00	4.29	5.53	5.78	
	10.00	5.82	7.53	8.00	
	13.00	12.9	16.1	18.6	
	16.00	29.0	31.1	38.8	
	20.00	79.2	72.0	94.0	
	25.00	230.	206.	260.	
	30.00	489.	602.		
DELTA K MAX	A: 34.01	710.			
	B: 34.23		1510.		
	C: 29.89			663.	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		22.88	18.36	17.00	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	1	1	1	
	1.25-2.0	1	1	1	
	>2.0				

CONDITION/HT: T81
 FORM: 0.10" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.098- 0.101"
 SPECIMEN WIDTH: 23.660- 23.820"
 REFERENCES: 86575

ALUM.
ALLOY

2024

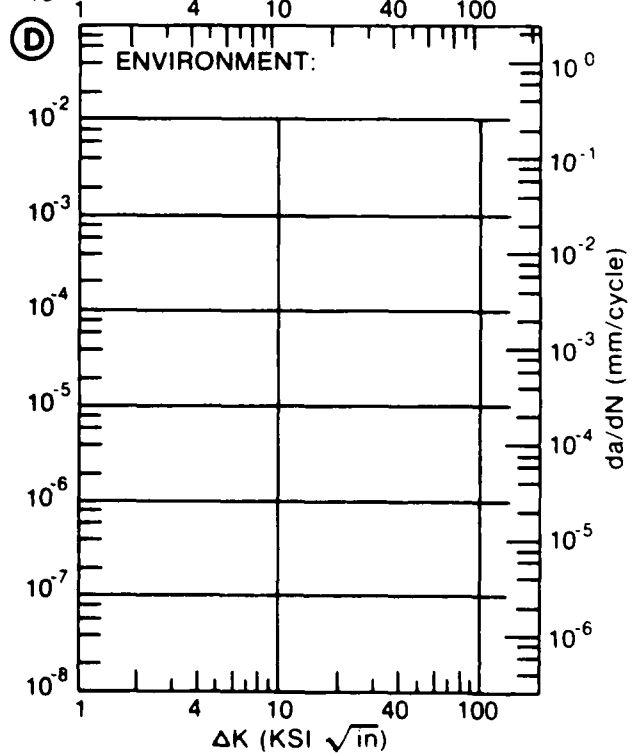
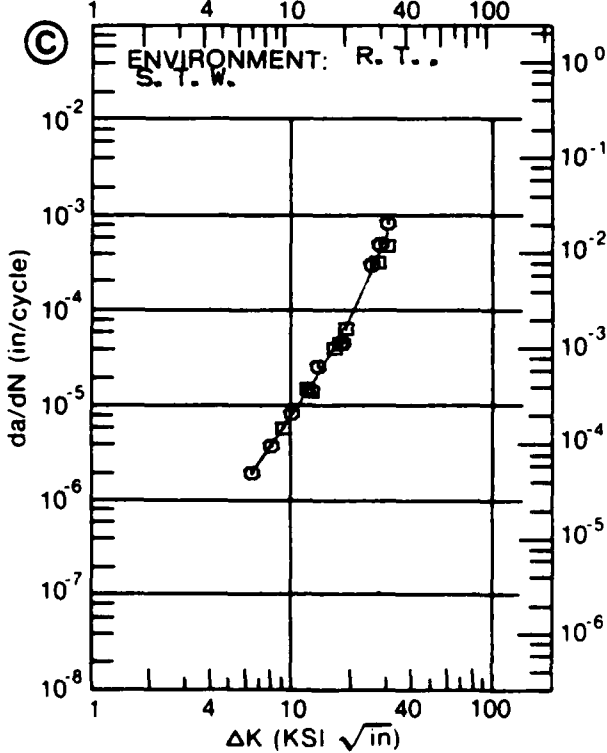
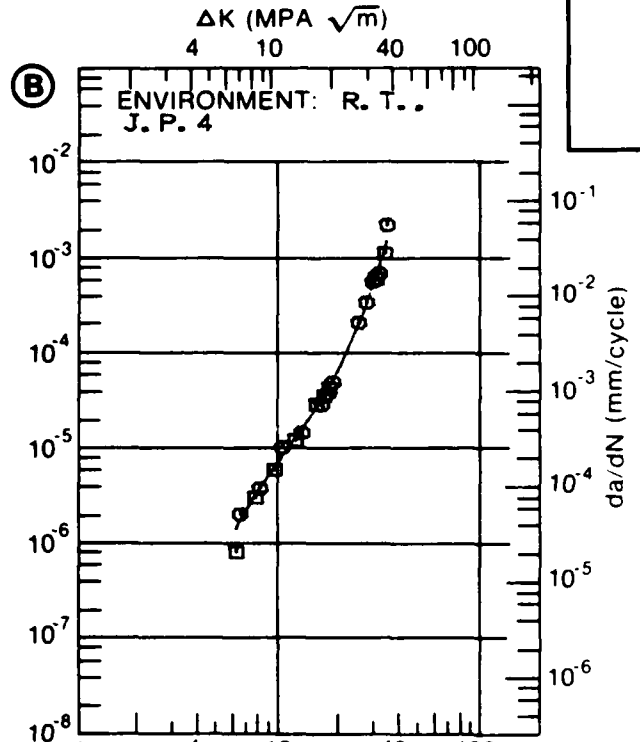
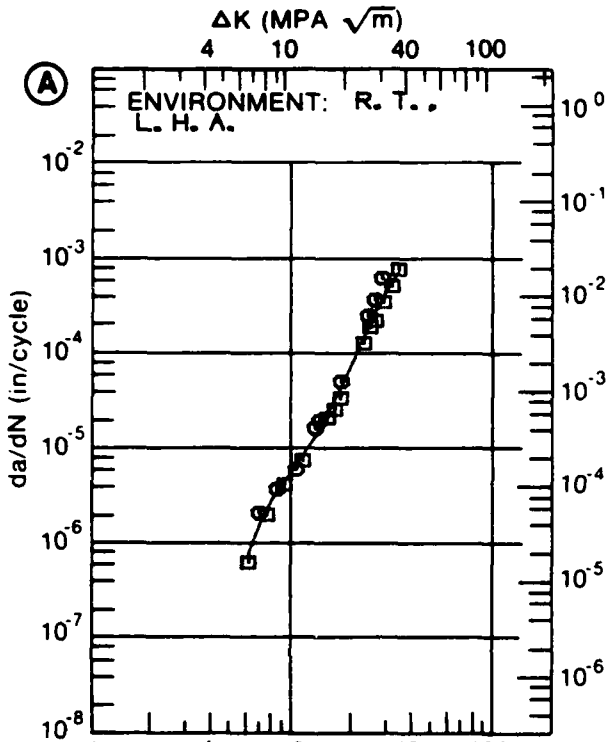


Figure 7.5.3.39

TABLE 7.5.3.40

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.40 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024	
CONDITION: TB1			
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)	
		A	B
		E= R. T. L. H. A. 6HZ	E= R. T. S. T. W. 1HZ
		C	D
DELTA K	A: 6.20	1.20	
MIN	B: 5.70		.75/
	C:		
	D:		
	6.00		1.03
	7.00	1.80	2.18
	8.00	2.69	3.57
	9.00	3.56	5.11
	10.00	4.34	6.83
	13.00	8.21	14.3
	16.00	20.6	30.7
	20.00	74.0	97.9
	25.00	303.	456.
	30.00	997.	979.
DELTA K	A: 31.13	1271.	
MAX	B: 31.22		983.
	C:		
	D:		
ROOT MEAN SQUARE		23.21	14.91
PERCENT ERROR			
LIFE	0.0-0.5		
PREDICTION	0.5-0.8		
RATIO	0.8-1.25	1	2
SUMMARY	1.25-2.0	1	
(NP/NA)	>2.0		

CONDITION/HT: T81
 FORM: 0.10" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 67.0 KSI
 ULT. STRENGTH: 73.0 KSI
 SPECIMEN THK: 0.099- 0.100"
 SPECIMEN WIDTH: 23.810- 23.910"
 REFERENCES: 86575

ALUM. ALLOY
2024

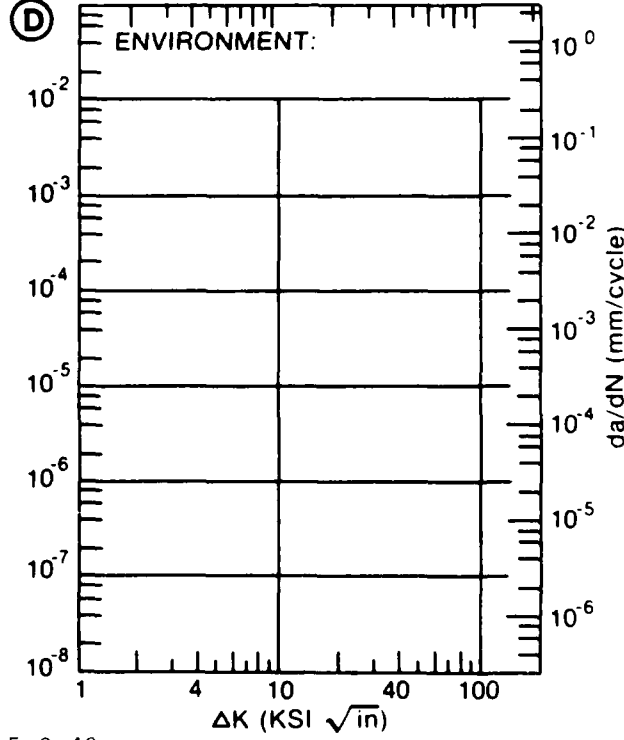
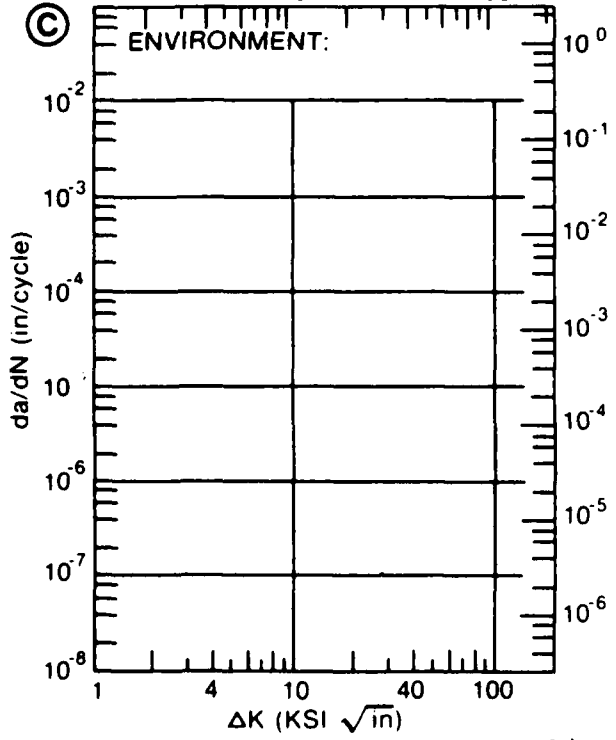
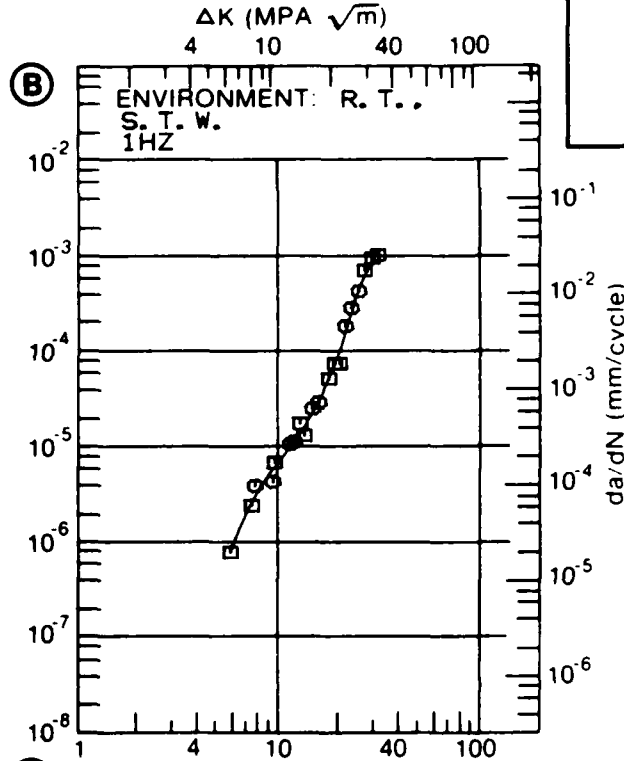
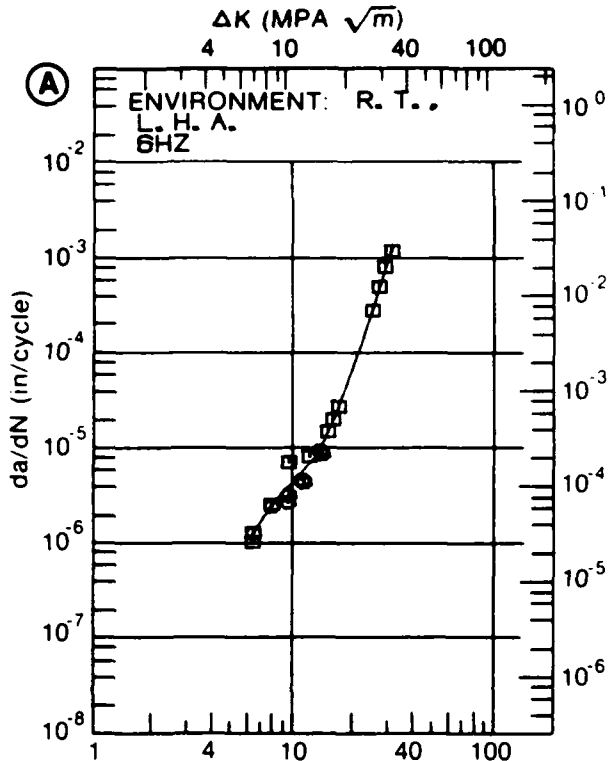


Figure 7.5.3.40

TABLE 7.5.3.41

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.41 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
ENVIRONMENT: R. T. , DRY AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-0.25	R=+0.10	R=+0.30	R=+0.50
DELTA K	A: 5.19	.542			
MIN	B: 5.48		1.57		
	C: 5.14			1.02	
	D: 2.94				.151
	3.00				.182
	3.50				.496
	4.00				.777
	5.00				1.26
	6.00	.892	1.61	1.89	2.21
	7.00	1.44	2.01	3.31	3.95
	8.00	2.15	2.79	5.16	6.64
	9.00	3.05	3.99	7.45	10.2
	10.00	4.17	5.65	10.2	14.8
	13.00	9.35	13.2	21.1	37.0
	16.00	18.7	24.7	36.7	84.5
	20.00	46.1	52.2	66.4	288.
	25.00		138.		
DELTA K	A: 24.54	146.			
MAX	B: 26.90		204.		
	C: 21.75			83.4	
	D: 21.91				556.
ROOT MEAN SQUARE		10.78	20.94	24.98	24.30
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25		1	1	
SUMMARY	1.25-2.0	1			1
(NP/NA)	>2.0				

CONDITION/HT: T81
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 65.3 KSI
 ULT. STRENGTH: 70.9 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM. ALLOY
2024

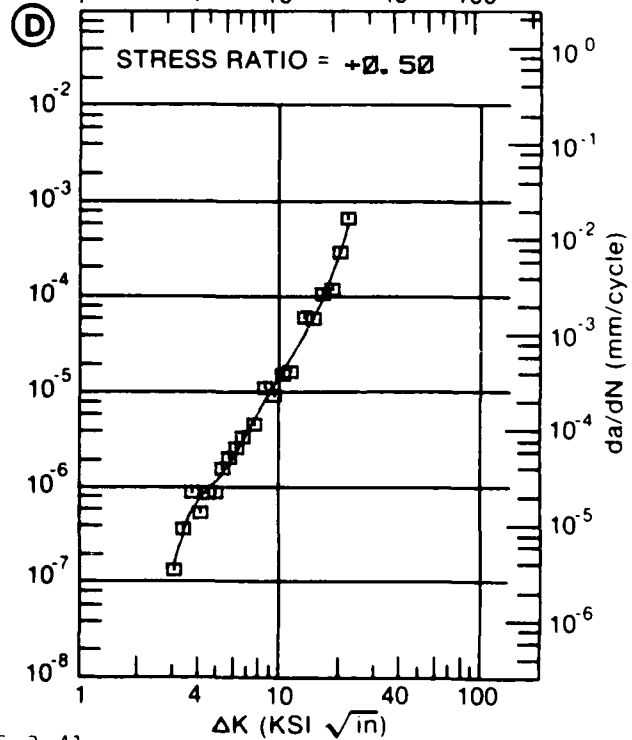
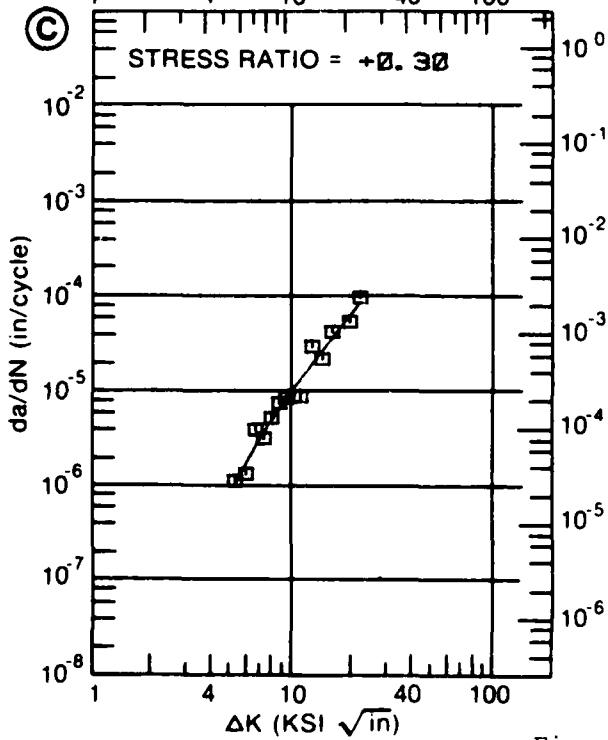
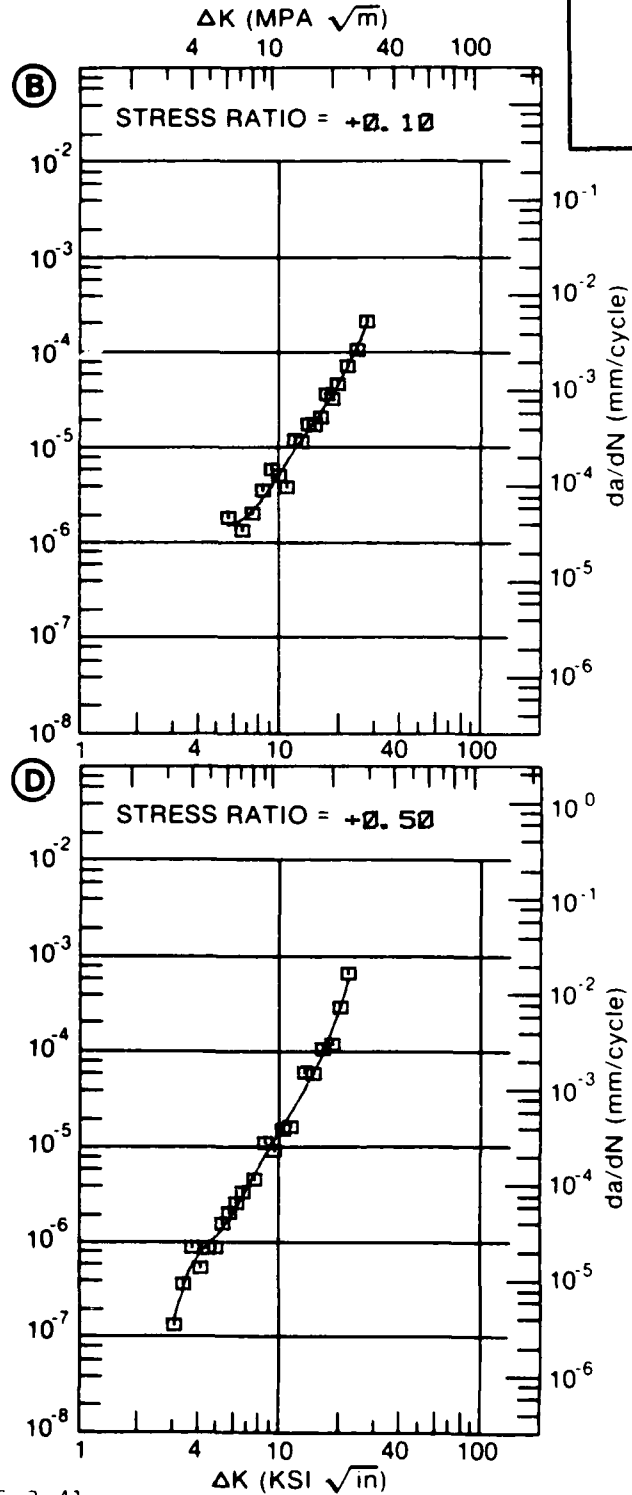
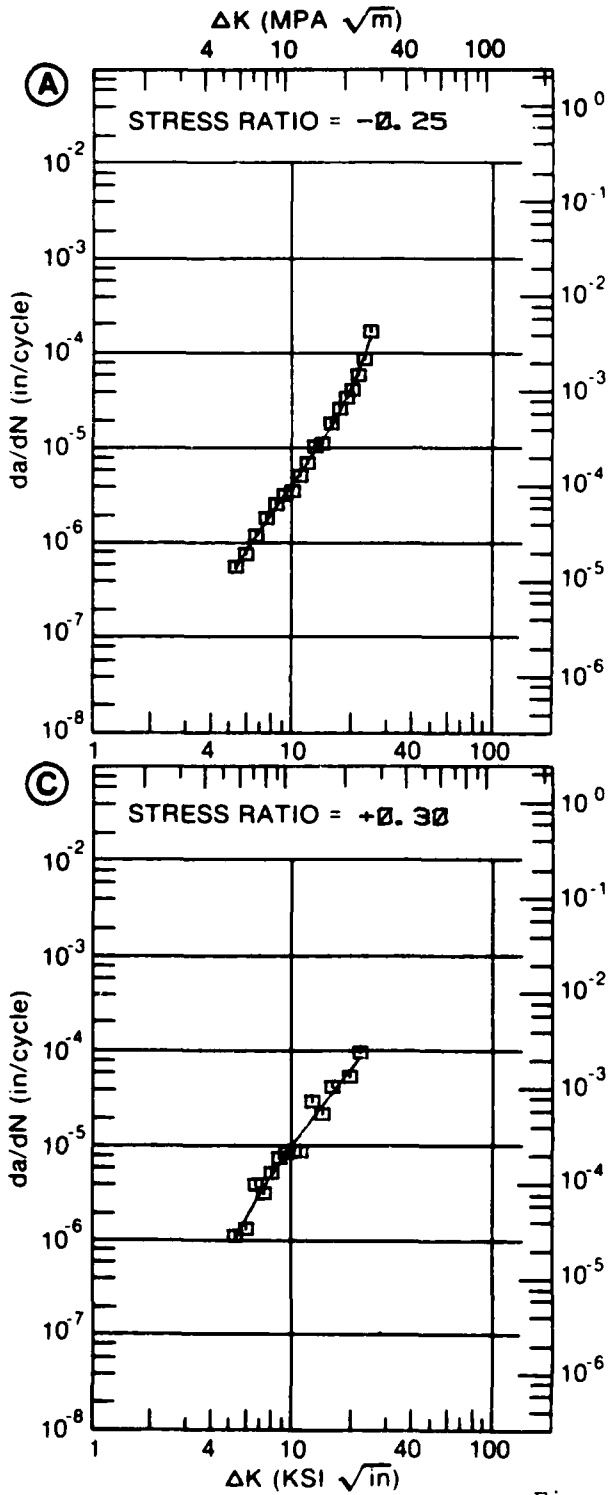


Figure 7.5.3.41

TABLE 7.5.3.42

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.42 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=-0.25	R=+0.10	R=+0.30	R=+0.50
A:	4.56	.206			
DELTA K B:	5.09		.783		
MIN C:	3.52			.206	
D:	3.89				.612
	4.00			.464	.685
	5.00	.289		1.04	1.50
	6.00	.675	1.25	1.99	2.76
	7.00	1.46	2.17	4.25	4.72
	8.00	2.70	3.62	8.07	7.60
	9.00	4.37	5.64	12.2	11.7
	10.00	6.45	8.15	15.2	17.2
	13.00	15.0	18.0	22.9	46.7
	16.00	26.9	32.4		115.
	20.00	51.3	70.1		
	25.00	118.	216.		
	30.00	302.	572.		
DELTA K A:	32.56	344.			
B:	32.48		682.		
MAX C:	14.10			29.1	
D:	19.90				360.
ROOT MEAN SQUARE		14.71	13.39	25.78	15.27
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				1
SUMMARY	1.25-2.0	1	1	1	
(NP/NA)	>2.0				

CONDITION/HT: T81
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 65.3 KSI
 ULT. STRENGTH: 70.9 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
ALLOY

2024

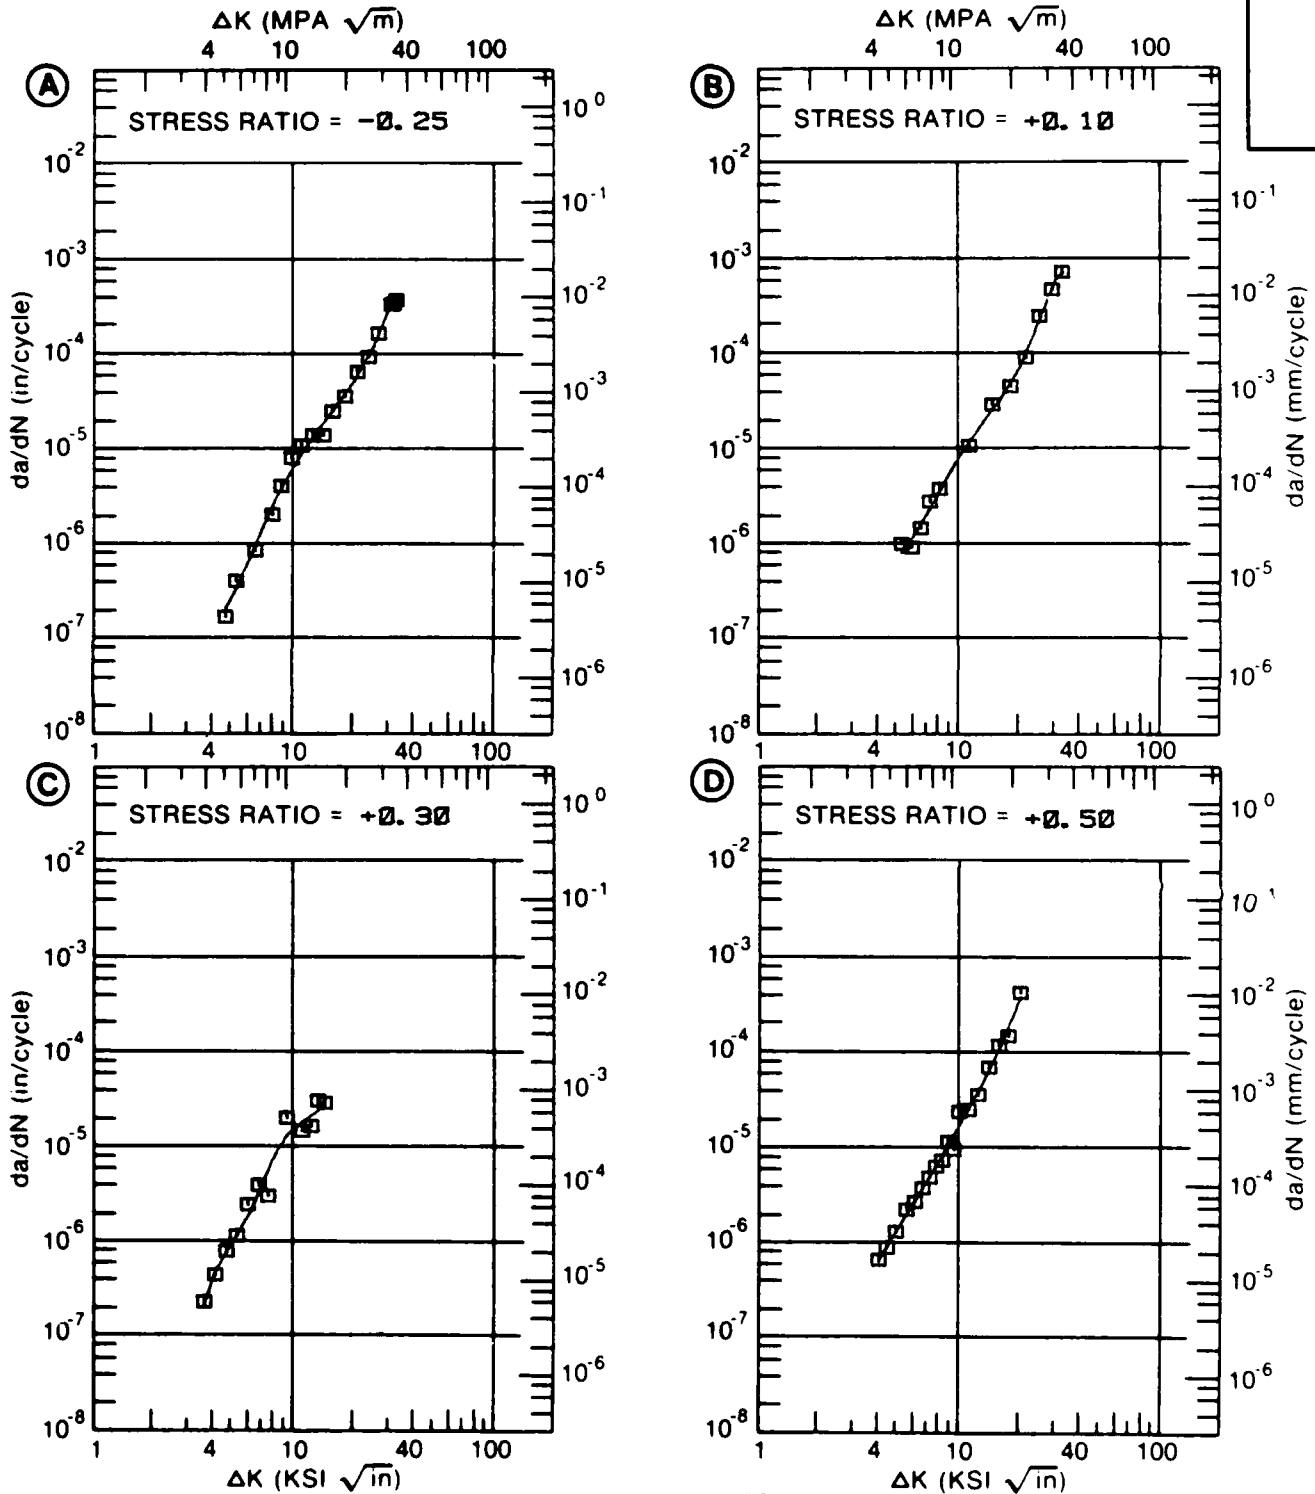


Figure 7.5.3.42

TABLE 7.5.3.43

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.43 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=-0.20	R=+0.10		
DELTA K	A: 4.03	.309			
MIN	B: 4.55		.196		
	C:				
	D:				
	5.00	.749	.365		
	6.00	1.56	1.04		
	7.00	2.87	2.19		
	8.00	4.82	3.82		
	9.00	7.56	5.86		
	10.00	11.2	8.25		
	13.00	29.2	16.7		
	16.00		26.4		
DELTA K	A: 15.95	59.3			
MAX	B: 18.76		36.2		
	C:				
	D:				
ABS. MEAN SQUARE		16.72	34.46		
PERCENT					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0	1	1		
(NP/NA)	>2.0		1		

CONDITION/HT: T81
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 65.3 KSI
 ULT. STRENGTH: 70.9 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
 ALLOY
 2024

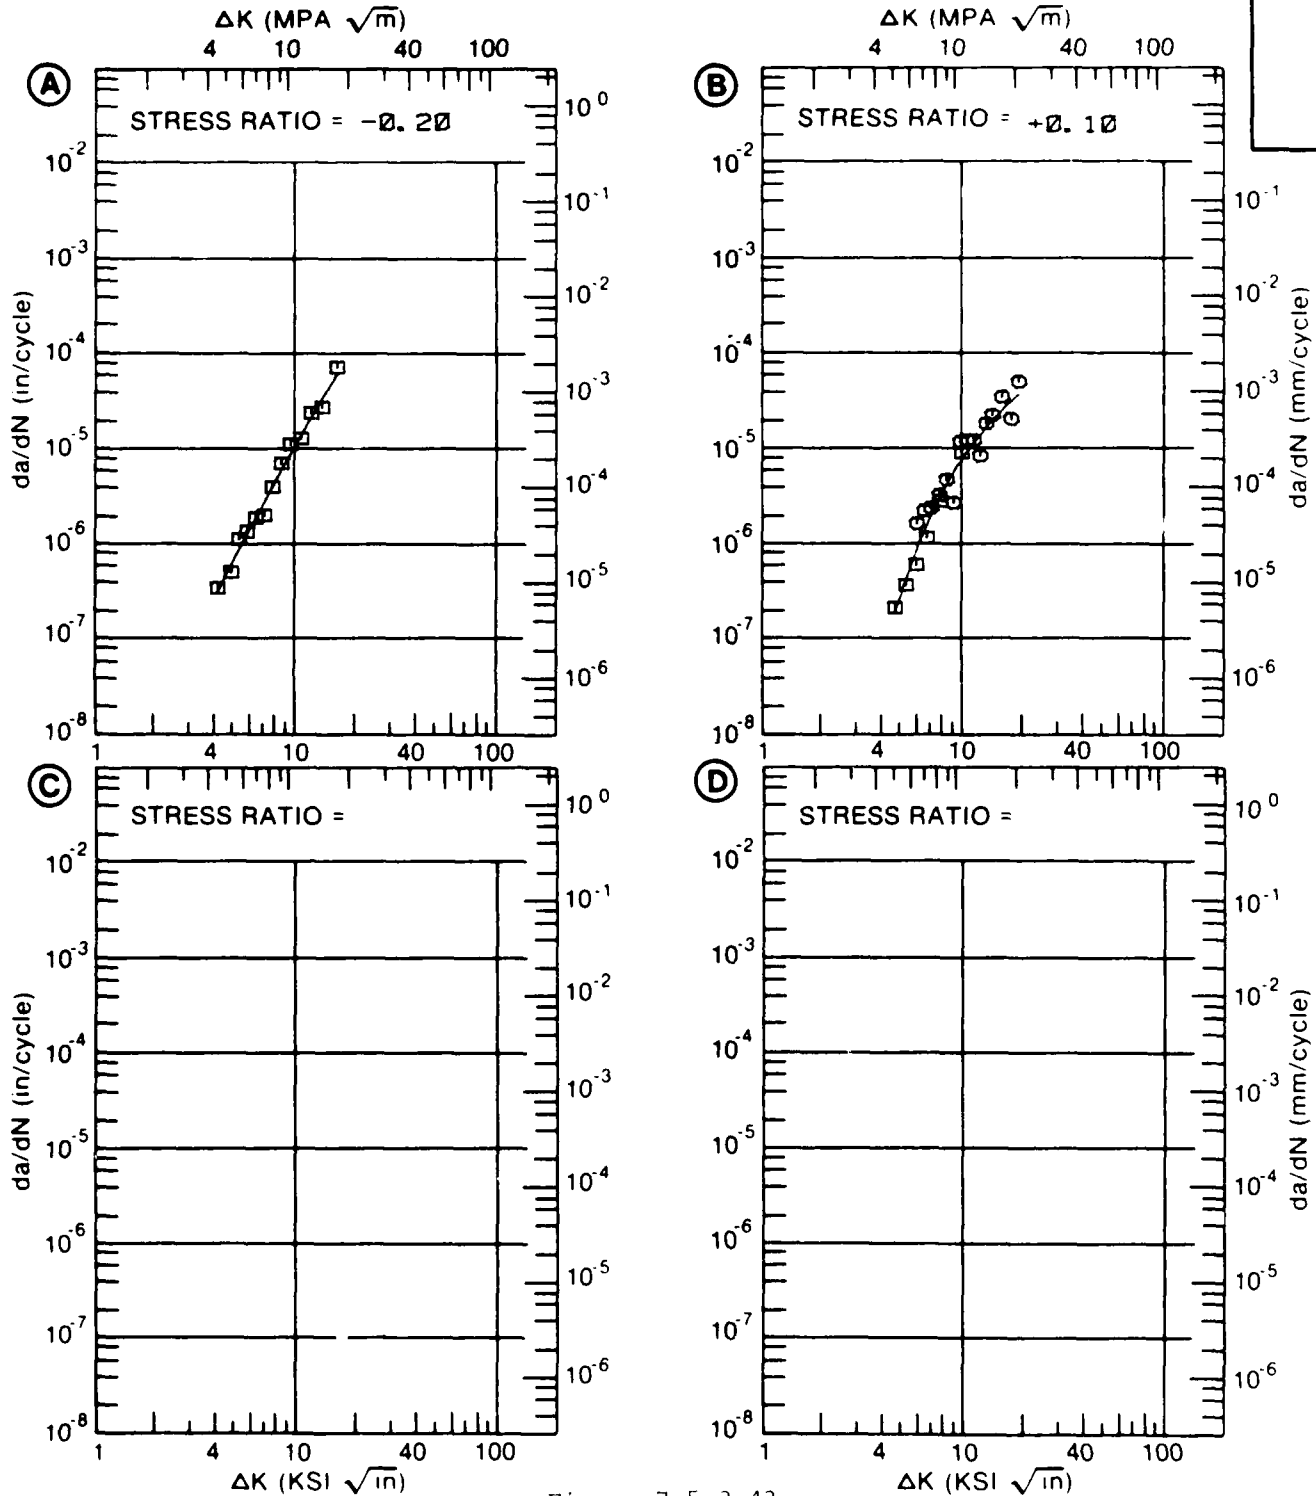


Figure 7.5.3.43

TABLE 7.5.3.44

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.44 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 0.10		F(HZ)= 1.00	
DELTA K	A: 5.09	1.14			
MIN	B: 5.09		.785		
	C:				
	D:				
	6.00	3.88	1.25		
	7.00	9.64	2.17		
	8.00	18.3	3.61		
	9.00	29.8	5.63		
	10.00	43.9	8.15		
	13.00	107.	18.2		
	16.00	232.	32.3		
	20.00		69.4		
	25.00		220.		
	30.00		565.		
DELTA K	A: 17.46	339.			
MAX	B: 32.48		681.		
	C:				
	D:				
ROOT MEAN SQUARE		43.37	13.16		
PERCENT ERROR					
LIFE PREDICTION RATIO	0.0-0.5				
SUMMARY (NP/NA)	0.5-0.8				
	0.8-1.25				
	1.25-2.0	1	1		
	>2.0				

CONDITION/HT: T81
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T. . H. H. A.

YIELD STRENGTH: 65.3 KSI
 ULT. STRENGTH: 70.9 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
ALLOY

2024

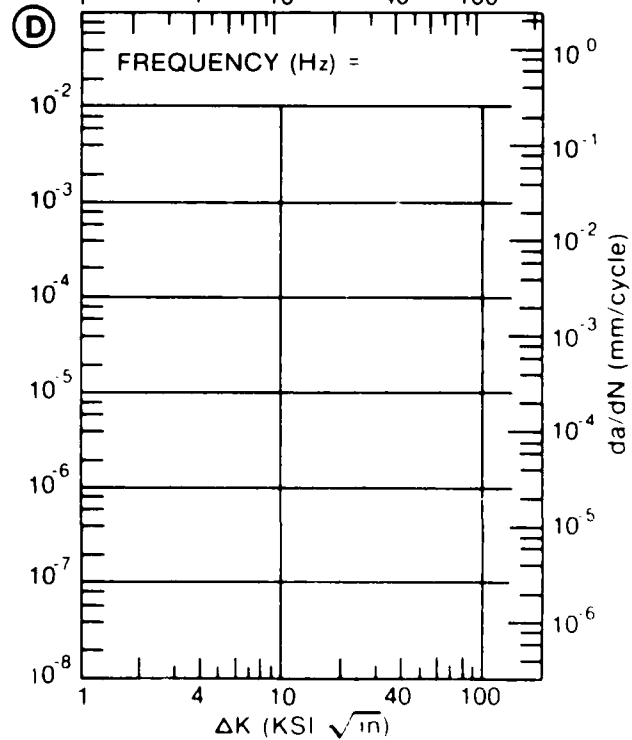
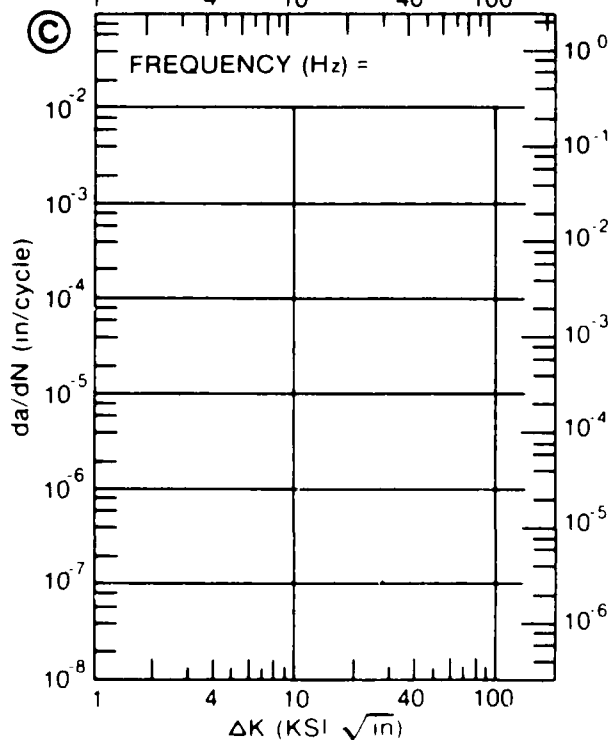
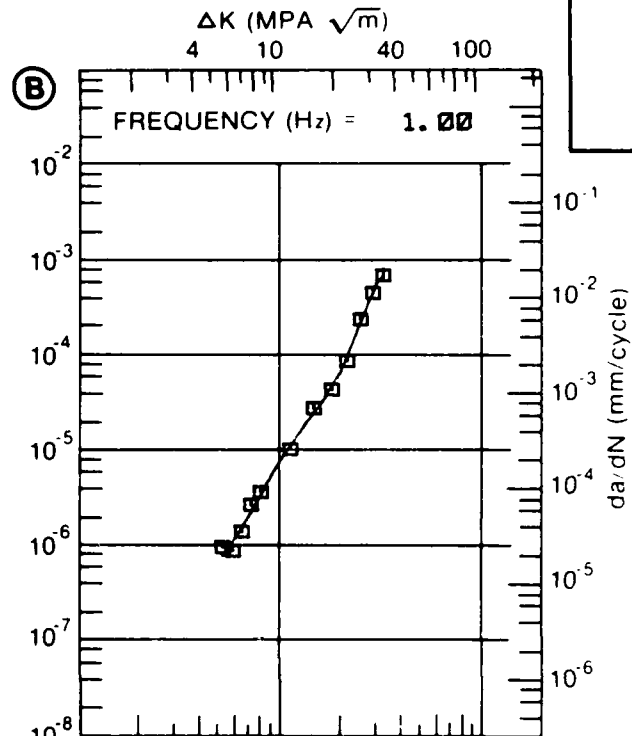
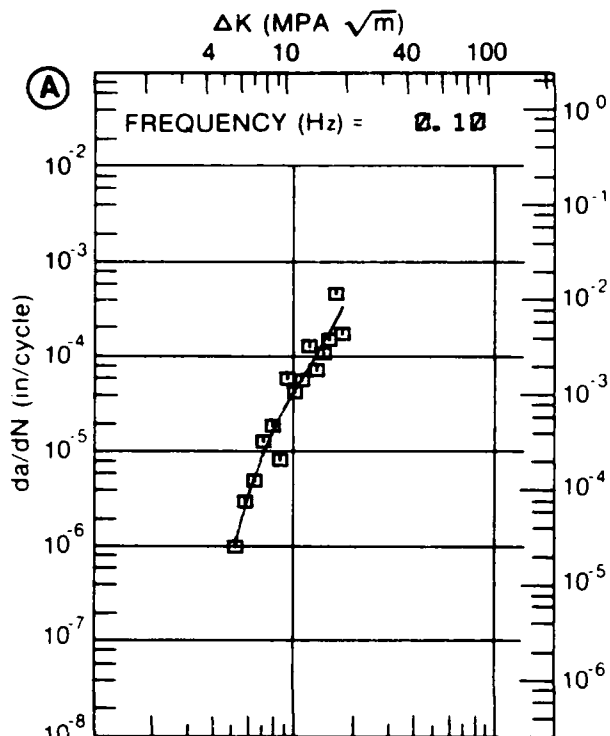


Figure 7.5.3.44

TABLE 7.5.3.45

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.45 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T81
ENVIRONMENT: R. T. , DRY AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=-0.25	R=+0.10		
DELTA K MIN	A: 5.21	.472			
	B: 5.26		.266		
	C:				
	D:				
	6.00	.653	.472		
	7.00	1.21	.831		
	8.00	1.98	1.41		
	9.00	2.85	2.31		
	10.00	3.81	3.51		
	13.00	7.82	9.93		
	16.00	16.1			
	20.00	48.3			
	25.00	209.			
	30.00	719.			
DELTA K MAX	A: 33.50	1351.			
	B: 13.58		18.7		
	C:				
	D:				

ROOT MEAN SQUARE 13.58 10.33
PERCENT ERROR

LIFE PREDICTION RATIO SUMMARY (NP/NA)

0.0-0.5		
0.5-0.8		
0.8-1.25		
1.25-2.0	1	1
>2.0		

CONDITION/HT: T81
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 65.8 KSI
 ULT. STRENGTH: 73.1 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
 ALLOY

2024

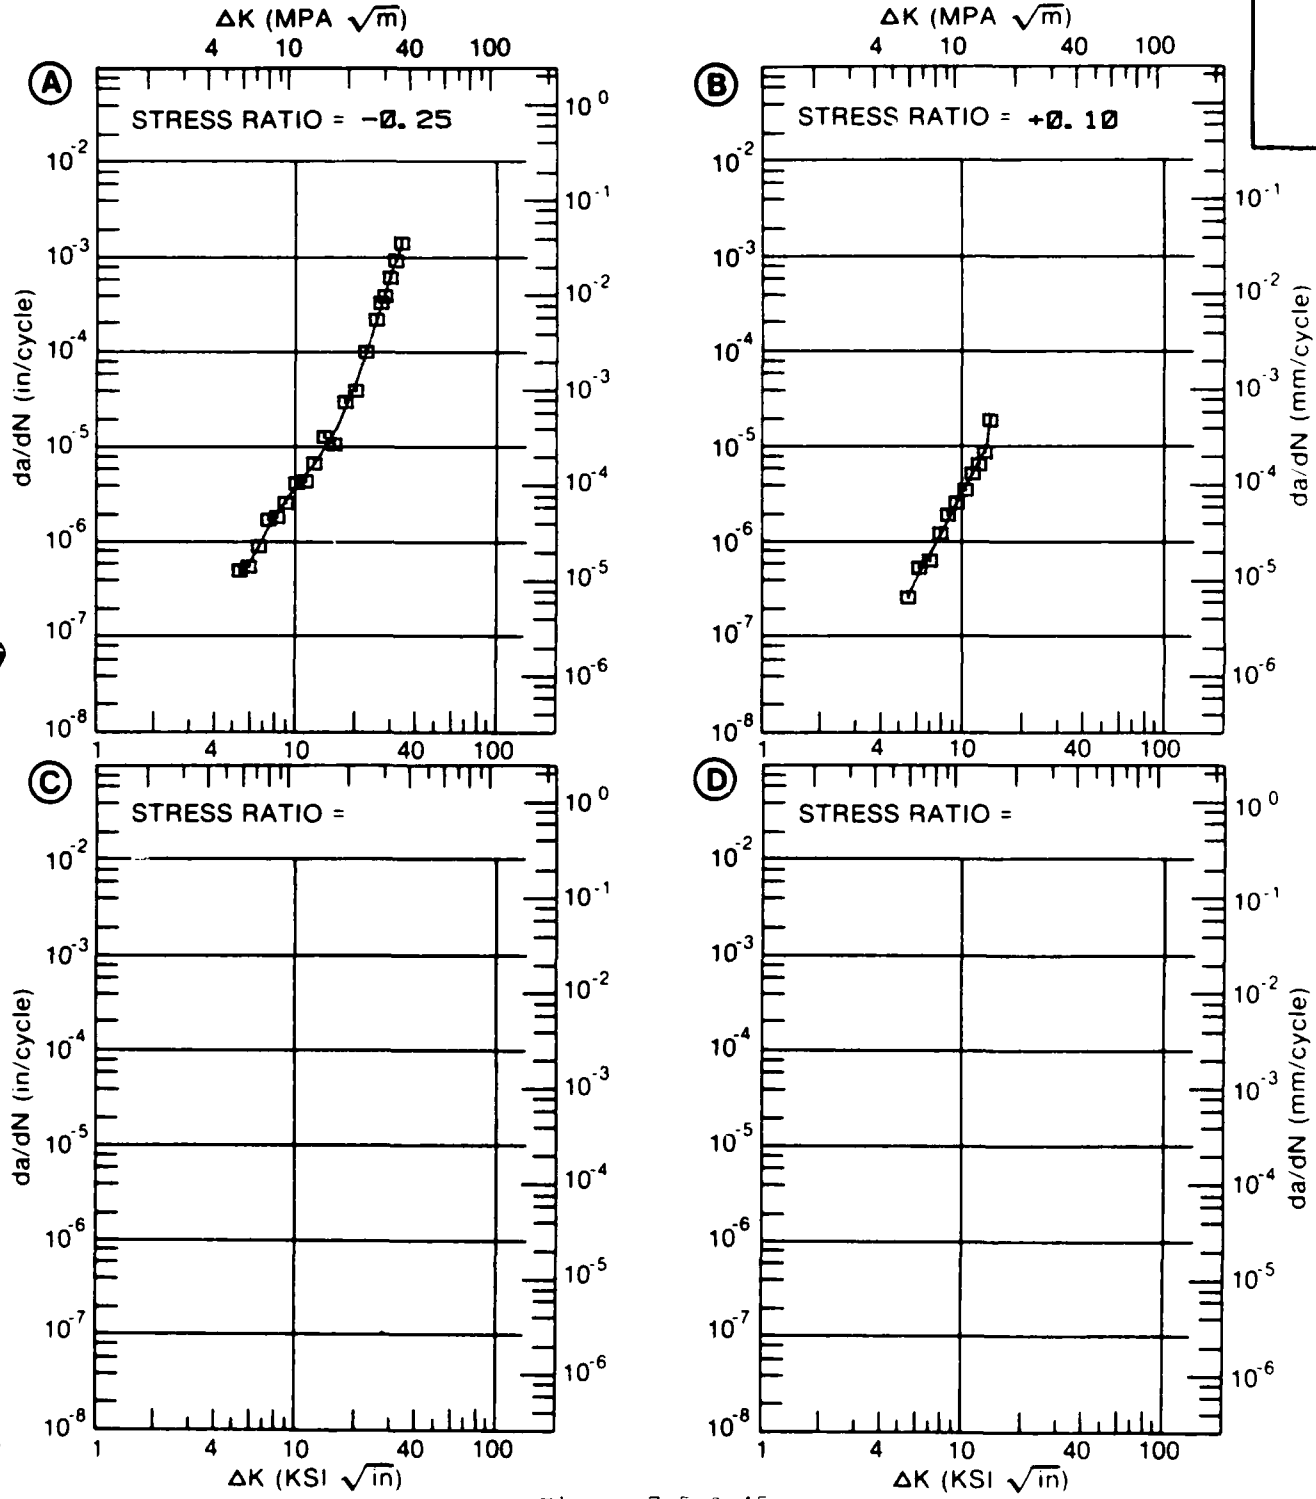


Figure 7.5.3.45

TABLE 7.5.3.46

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.46 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T81					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=-0.25	R=+0.10	R=+0.50	
DELTA K	A: 5.22	1.04			
MIN	B: 5.53		.551		
	C: 2.80			.0957	
	D:				
	3.00			.175	
	3.50			.451	
	4.00			.756	
	5.00			1.44	
	6.00	1.53	.870	2.66	
	7.00	2.13	1.86	4.78	
	8.00	2.77	3.16	8.20	
	9.00	3.62	4.66	13.6	
	10.00	4.89	6.37	22.2	
	13.00	13.8	14.4	90.5	
	16.00	32.8	35.8	283.	
	20.00	64.7	129.		
	25.00		435.		
DELTA K	A: 23.07	121.			
MAX	B: 28.46		634.		
	C: 18.14			467.	
	D:				
ROOT MEAN SQUARE		21.79	13.25	14.02	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0	1	1	1	
(NP/NA)	>2.0				

CONDITION/HT: T81
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 65.8 KSI
 ULT. STRENGTH: 73.1 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
ALLOY

2024

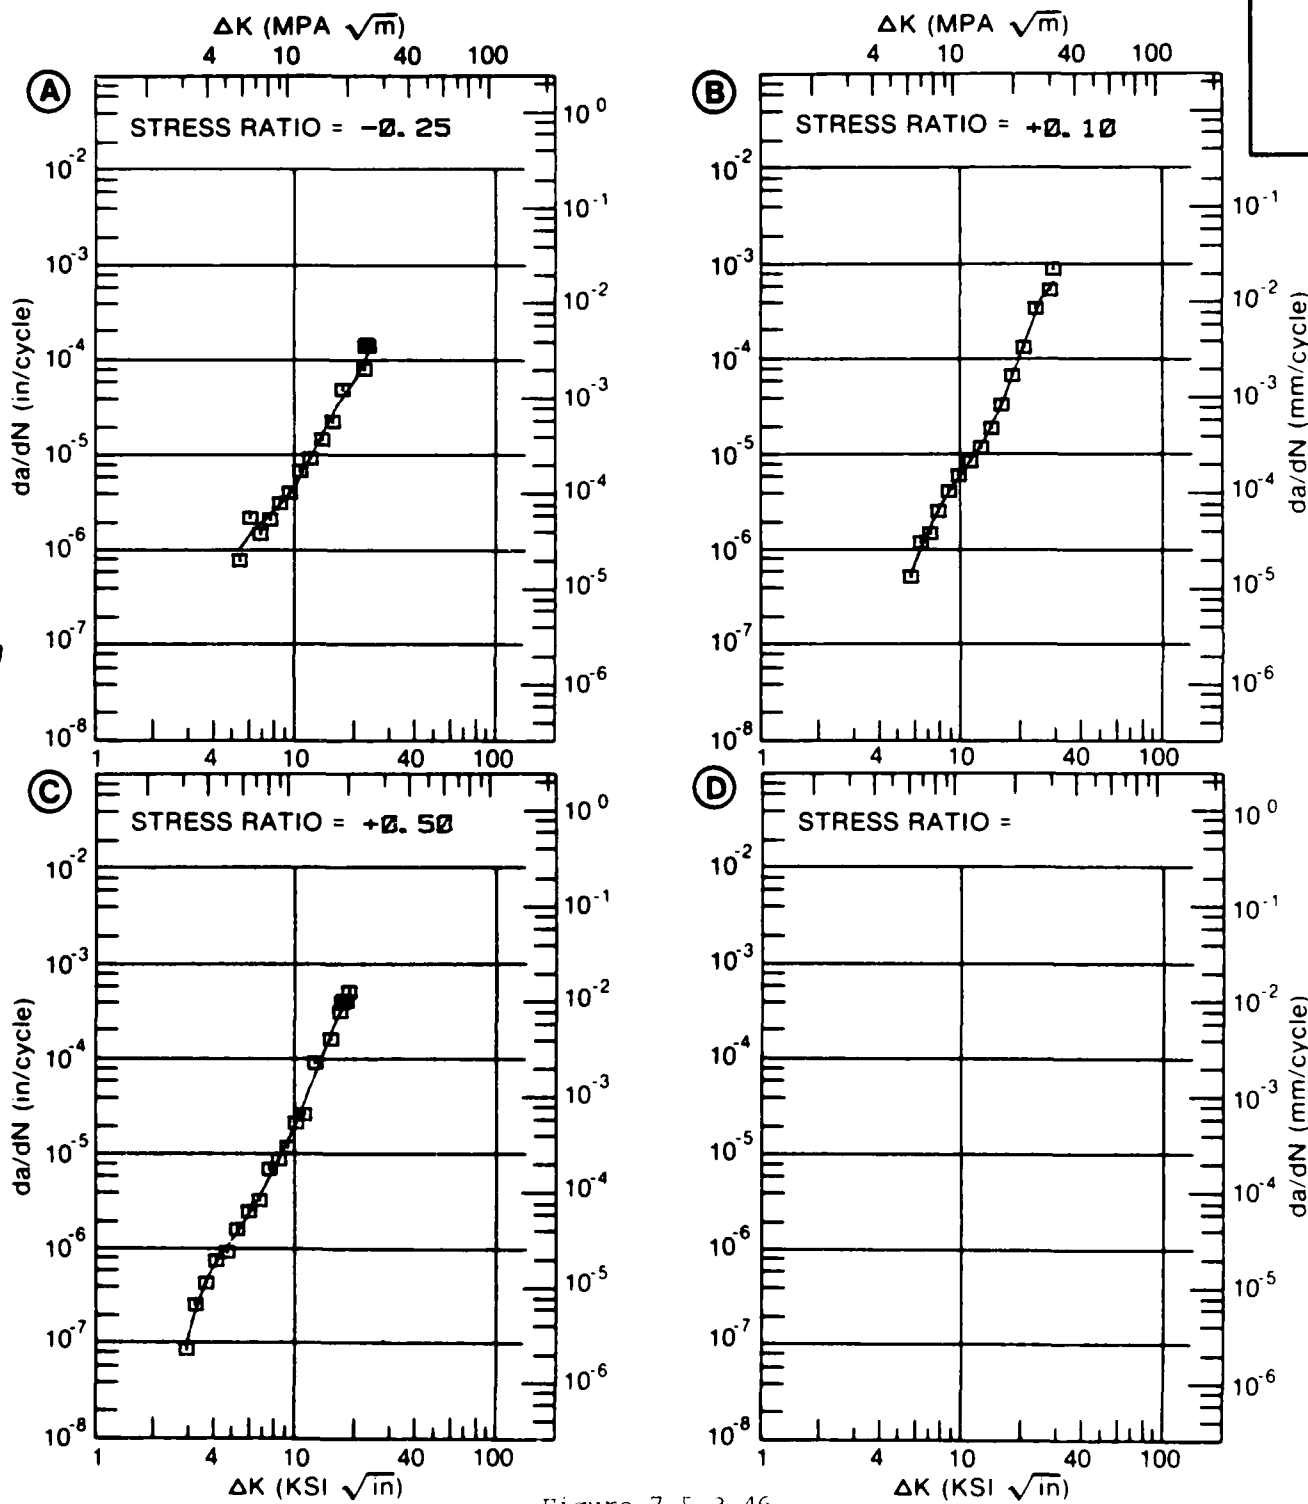


Figure 7.5.3.46

TABLE 7.5.3.47

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.47 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: TB1					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30		
DELTA K A:	4.03	.094			
DELTA K B:	7				
MIN C:					
D:					
	5.00	.395			
	6.00	1.03			
	7.00	2.03			
	8.00	3.38			
	9.00	5.12			
	10.00	7.27			
	13.00	17.3			
	16.00	37.2			
	20.00	101.			
DELTA K A:	20.39	111.			
DELTA K B:					
MAX C:					
D:					
ROOT MEAN SQUARE		34.62	0.00		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0	1			

CONDITION/HT: T81
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 65.8 KSI
 ULT. STRENGTH: 73.1 KSI
 SPECIMEN THK: 0.125"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: GD004

ALUM.
 ALLOY

2024

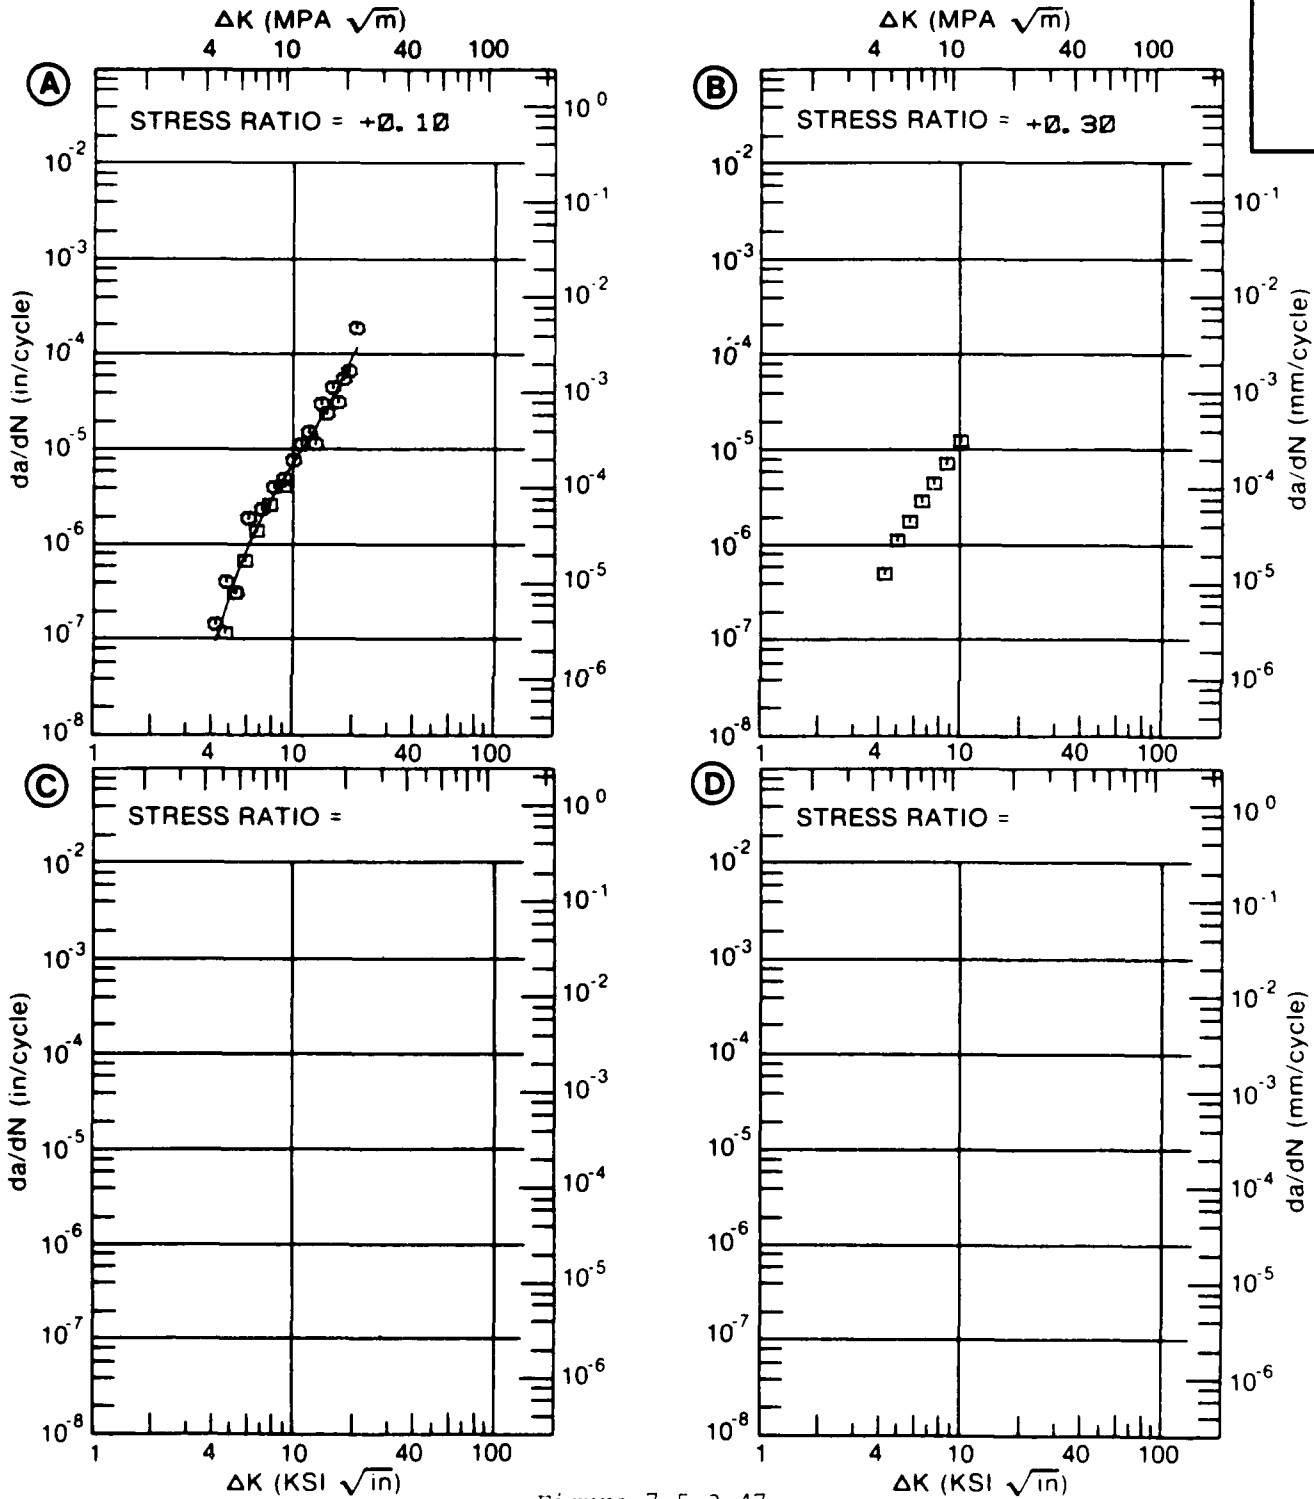


Figure 7.5.3.47

TABLE 7.5.3.48

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.48 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 5.47	.653			
MIN	B:				
	C:				
	D:				
	6.00	1.37			
	7.00	3.08			
	8.00	4.49			
	9.00	5.33			
	10.00	5.84			
	13.00	8.06			
DELTA K	A: 15.84	16.5			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		11.86			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: L-S
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.374 - 0.377"
 SPECIMEN WIDTH: 5.004 - 5.006"
 REFERENCES: 90981

ALUM. ALLOY
2024

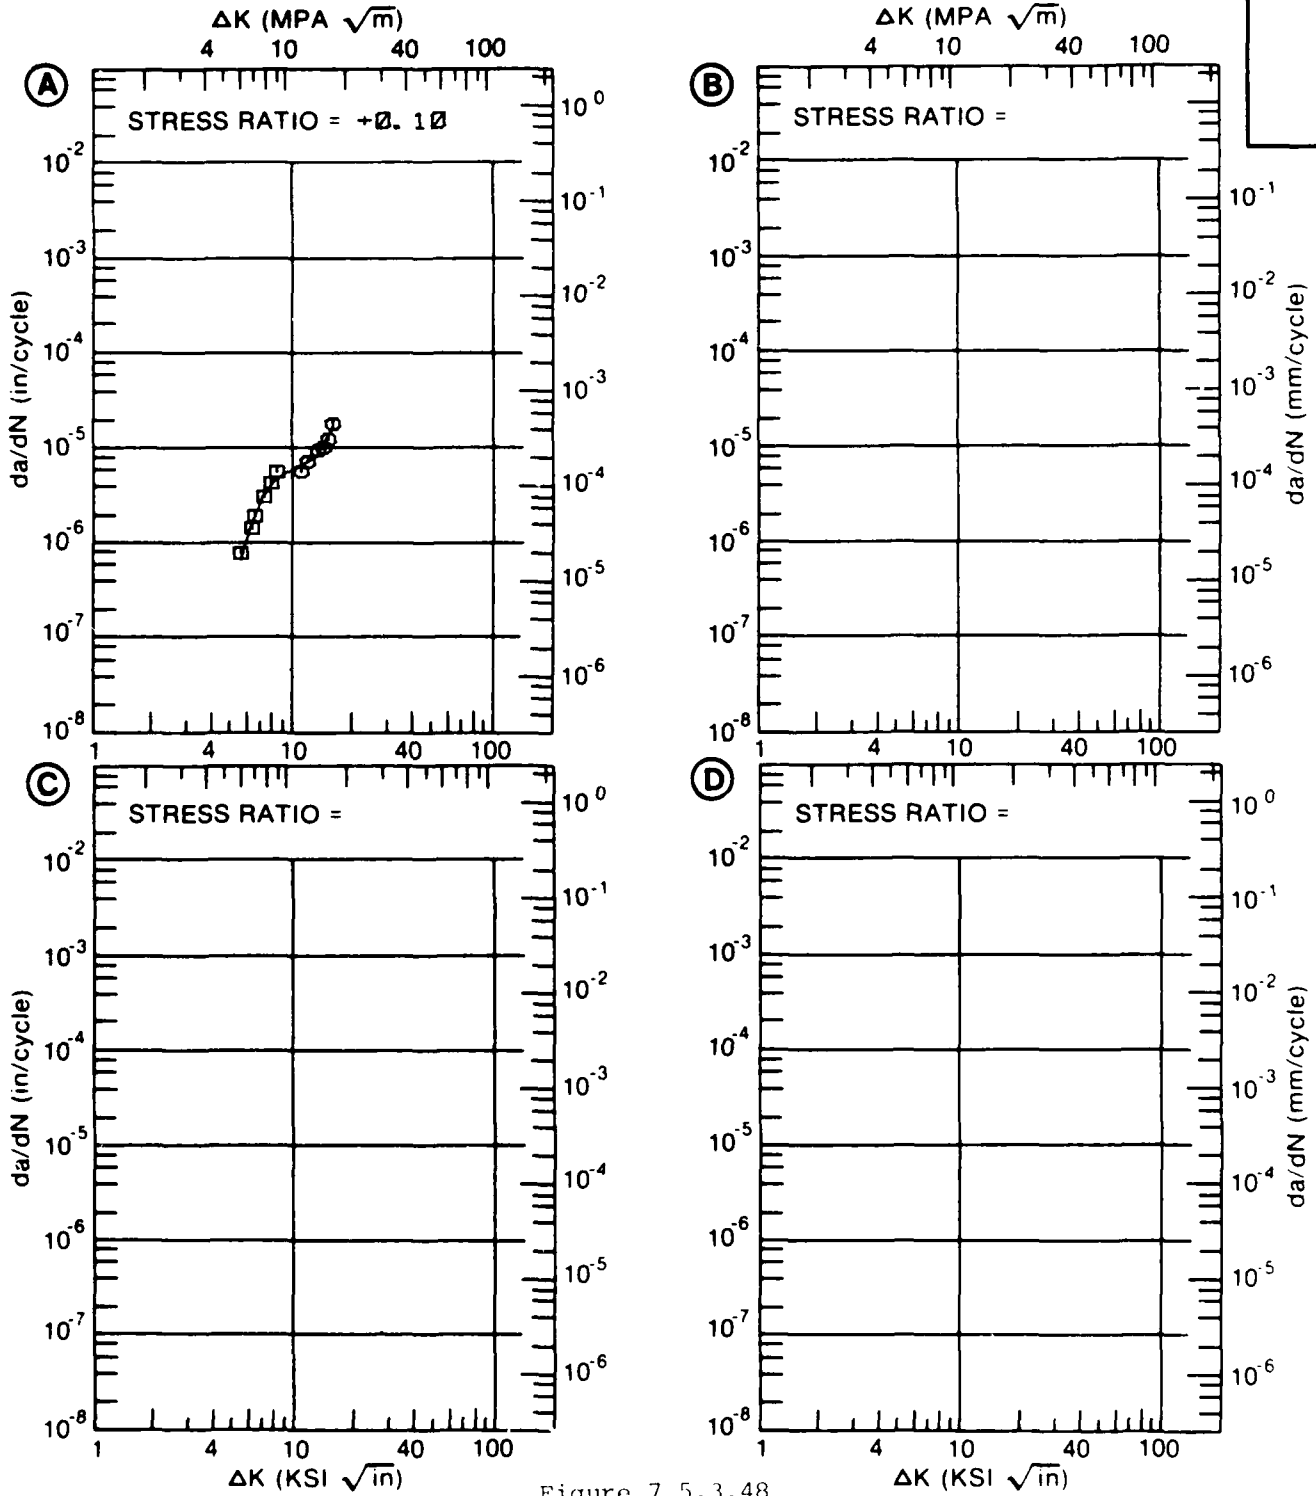


Figure 7.5.3.48

TABLE 7.5.3.49

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.49 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T851
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	R=+0.10	R=+0.50		
DELTA K A: 3.37	.24			
MIN B:				
C:				
D:				
3.50	.259			
4.00	.328			
5.00	.576			
6.00	1.01			
7.00	1.66			
8.00	2.55			
9.00	3.65			
10.00	4.87			
13.00	9.08			
16.00	17.2			
DELTA K A: 16.73	33.8			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 21.69 0.00
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.376- 0.380"
 SPECIMEN WIDTH: 5.003- 5.006"
 REFERENCES: 90981

ALUM.
ALLOY

2024

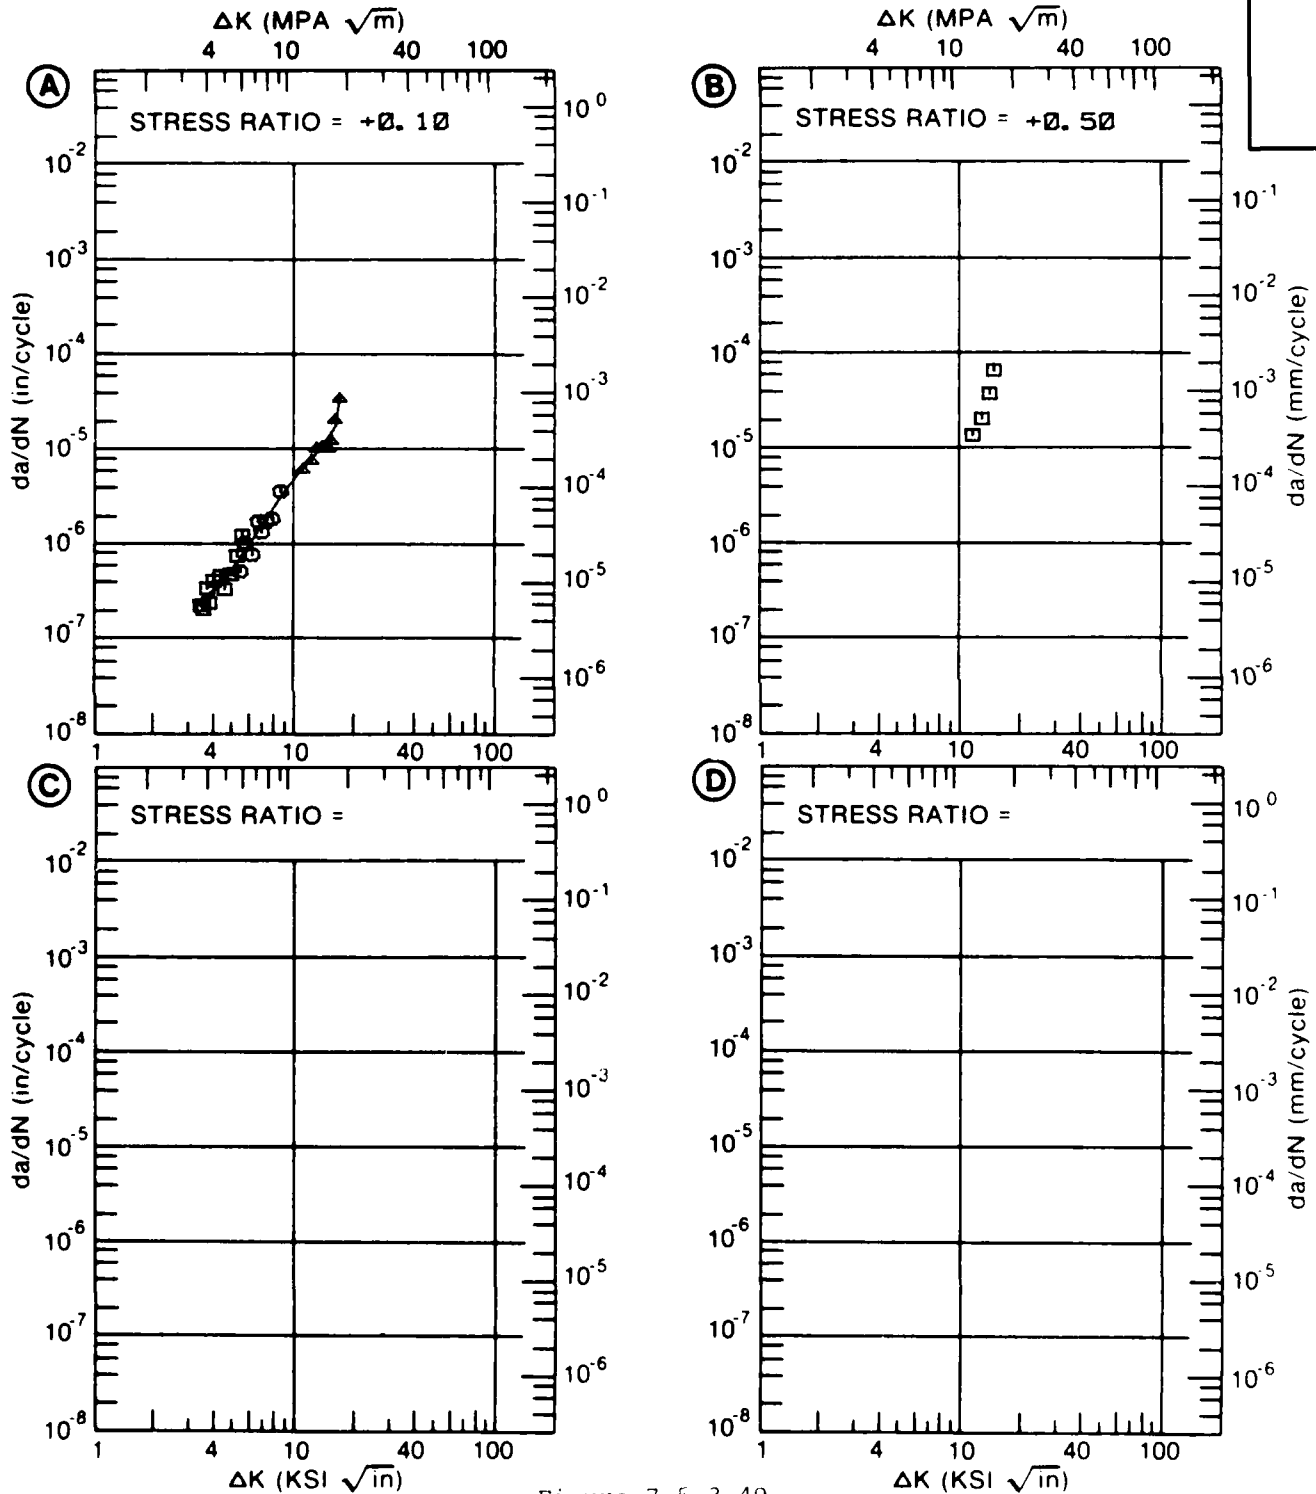


Figure 7.5.3.49

TABLE 7.5.3.50

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.50 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , 3.5% NaCl					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 5.15	.421			
MIN	B: 3.28		.245		
	C:				
	D:				
	3.50		.286		
	4.00		.426		
	5.00		.960		
	6.00	.958	1.94		
	7.00	1.95	3.38		
	8.00	3.30	5.07		
	9.00	4.92	6.91		
	10.00	6.73	9.96		
	13.00	12.3			
DELTA K	A: 13.84	13.8			
MAX	B: 10.28		11.3		
	C:				
	D:				
ROOT MEAN SQUARE		33.64	26.04		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.377- 0.380"
 SPECIMEN WIDTH: 5.002- 5.005"
 REFERENCES: 90981

ALUM. ALLOY
2024

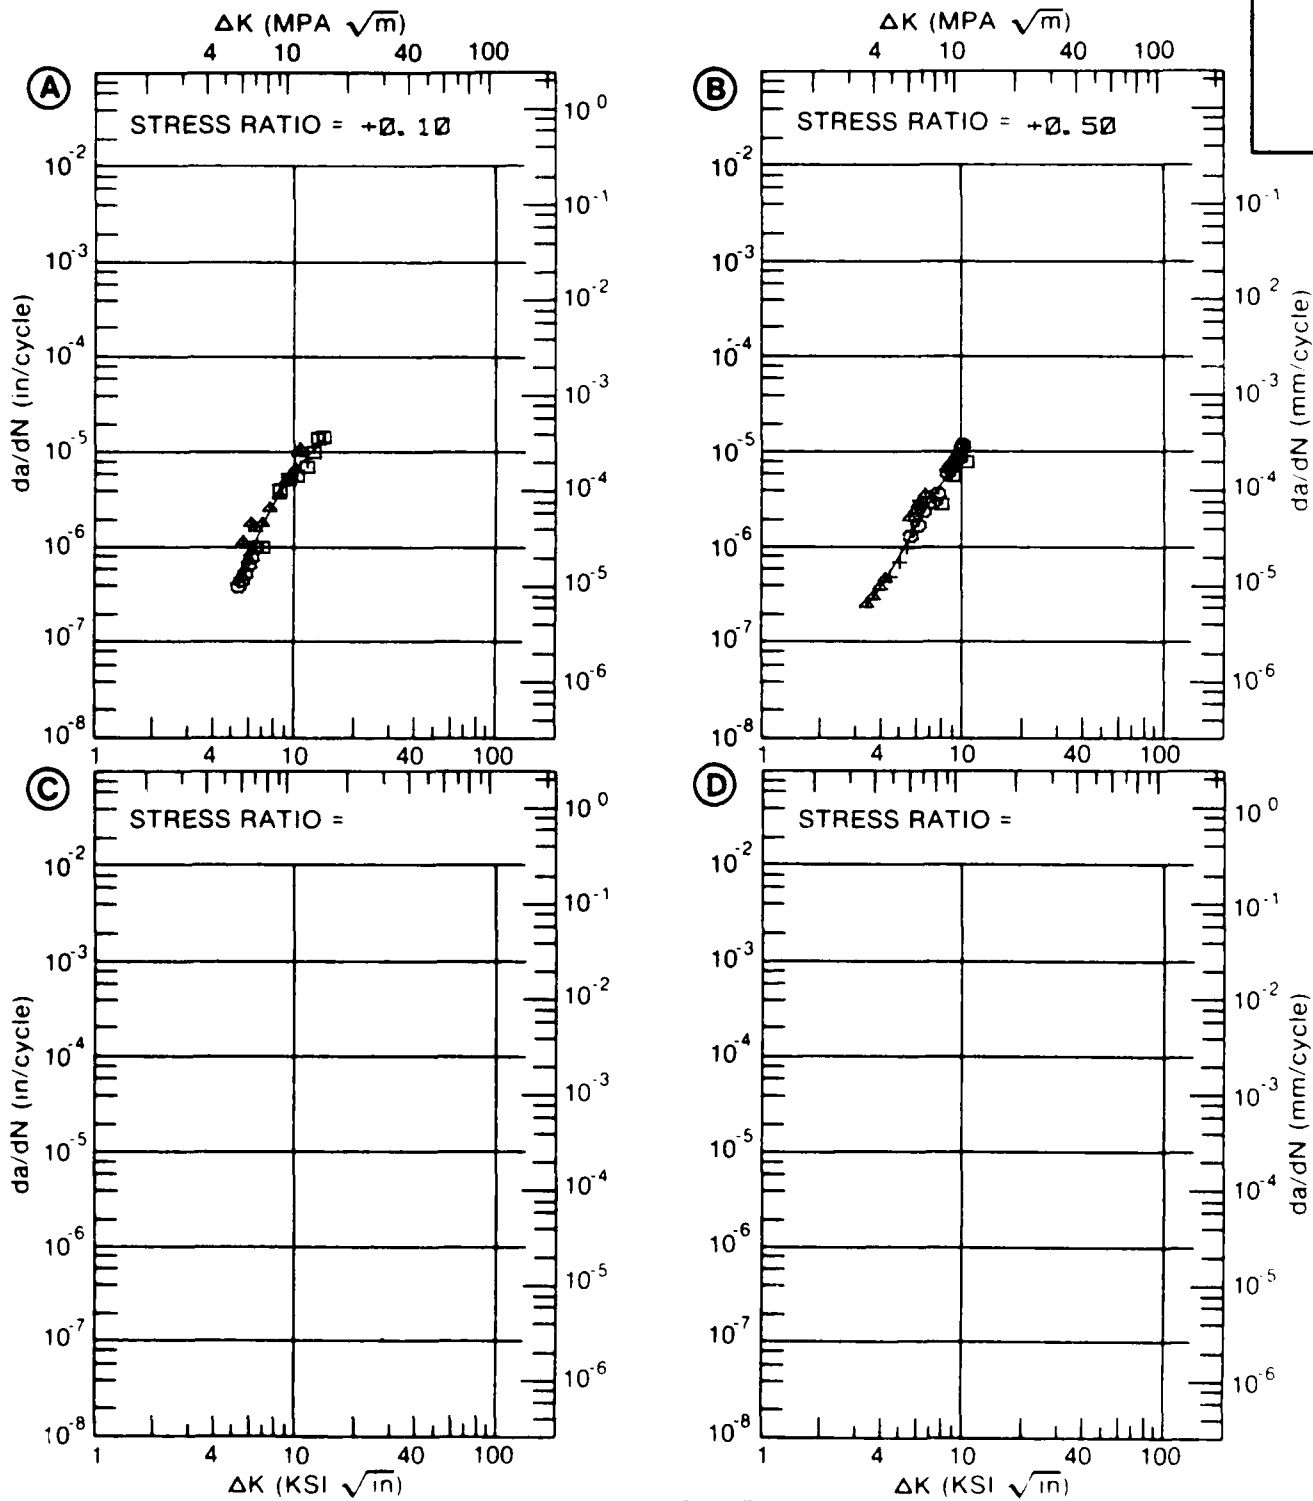


Figure 7.5.3.50

TABLE 7.5.3.51

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.51 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T851
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 8.03	3.73			
MIN	B: 2.48		.187		
	C:				
	D:				
	2.50		.176		
	3.00		.140		
	3.50		.298		
	4.00		.564		
	5.00		1.31		
	6.00		2.79		
	7.00		5.94		
	8.00		10.8		
	9.00	5.50	15.4		
	10.00	7.38	17.2		
	13.00	19.5			
	16.00	39.2			
	20.00	71.4			
DELTA K	A: 22.79	166.			
MAX	B: 10.53		16.5		
	C:				
	D:				

ROOT MEAN SQUARE 11.73 16.85
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 66.6 KSI
 ULT. STRENGTH: 72.0 KSI
 SPECIMEN THK: 0.375"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

ALUM.
ALLOY

2024

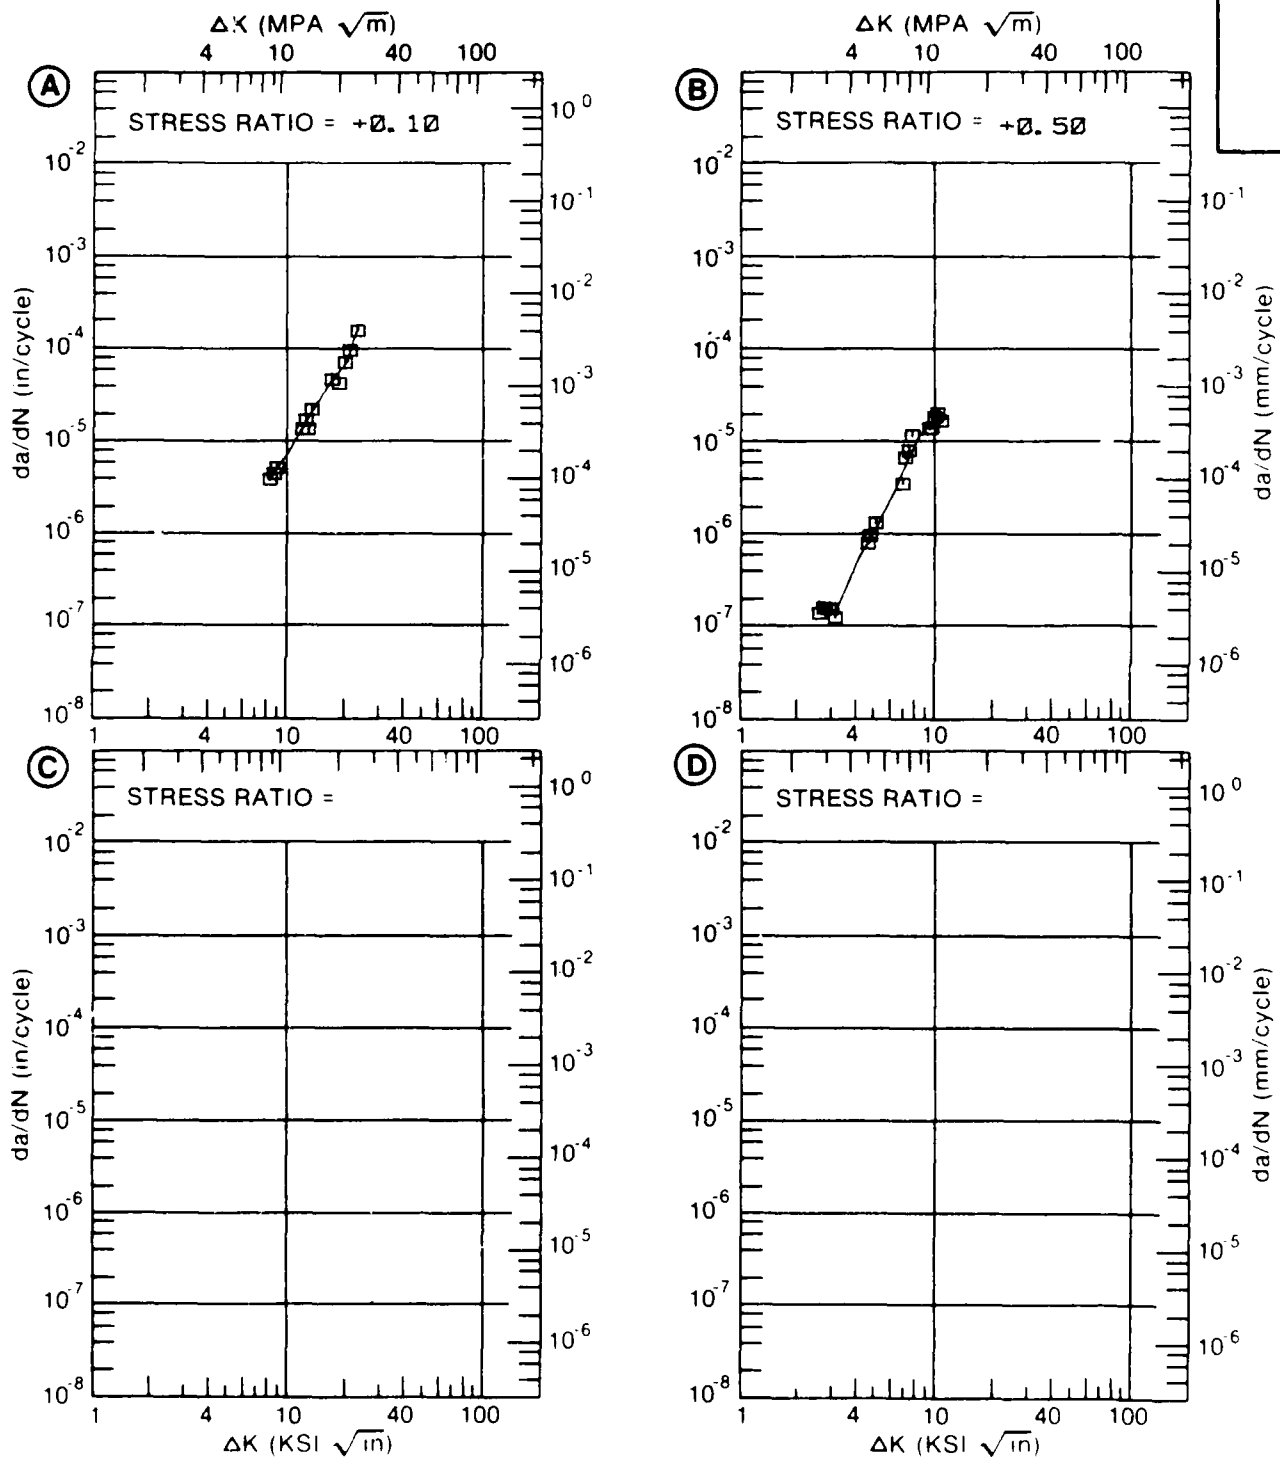


Figure 7.5.3.51

TABLE 7.5.3.52

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.52 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T851
ENVIRONMENT: R. T. , 3.5% NAACL

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A:	4.70	1.16		
	B:				
	C:				
	D:				
		5.00	1.47		
		6.00	2.70		
		7.00	4.24		
		8.00	6.10		
		9.00	8.34		
		10.00	11.1		
	13.00	23.6			
	16.00	48.4			
	20.00	126.			
	25.00	428.			
DELTA K MAX	A:	28.22	952.		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 13.07
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 0.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 66.6 KSI
 ULT. STRENGTH: 72.0 KSI
 SPECIMEN THK: 0.375"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

ALUM.
ALLOY

2024

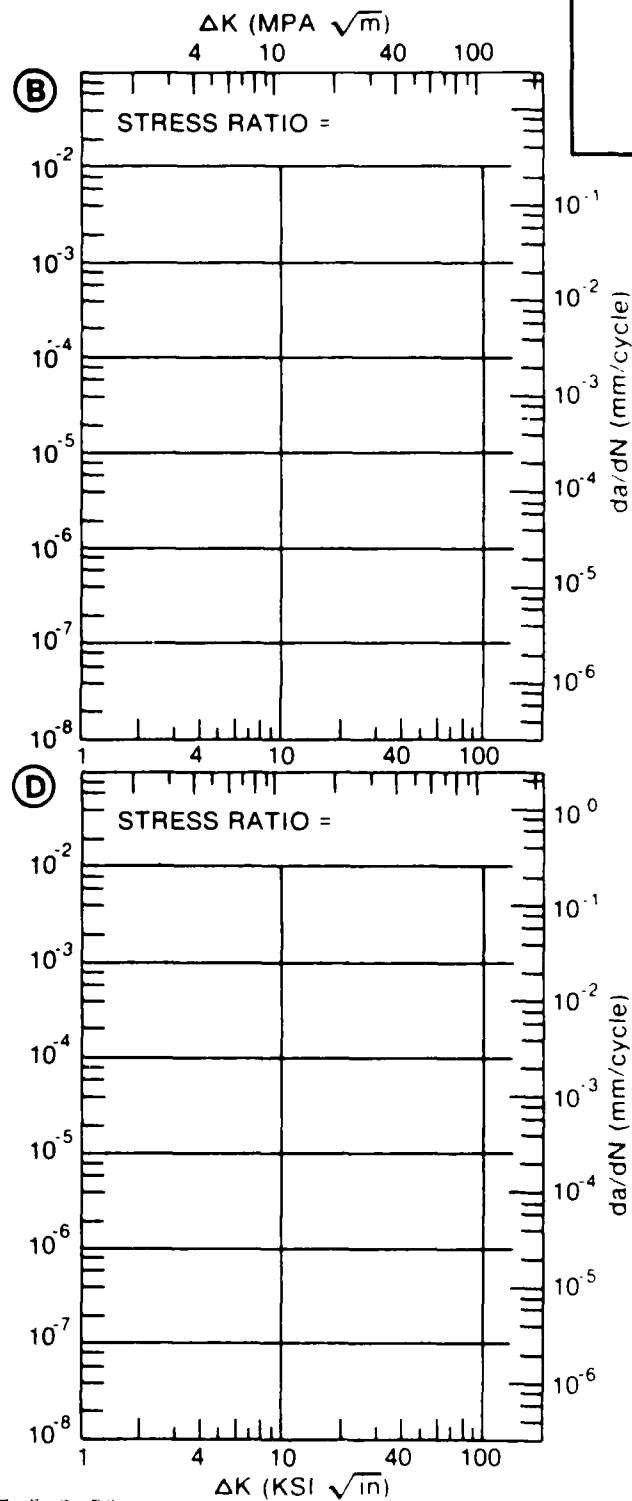
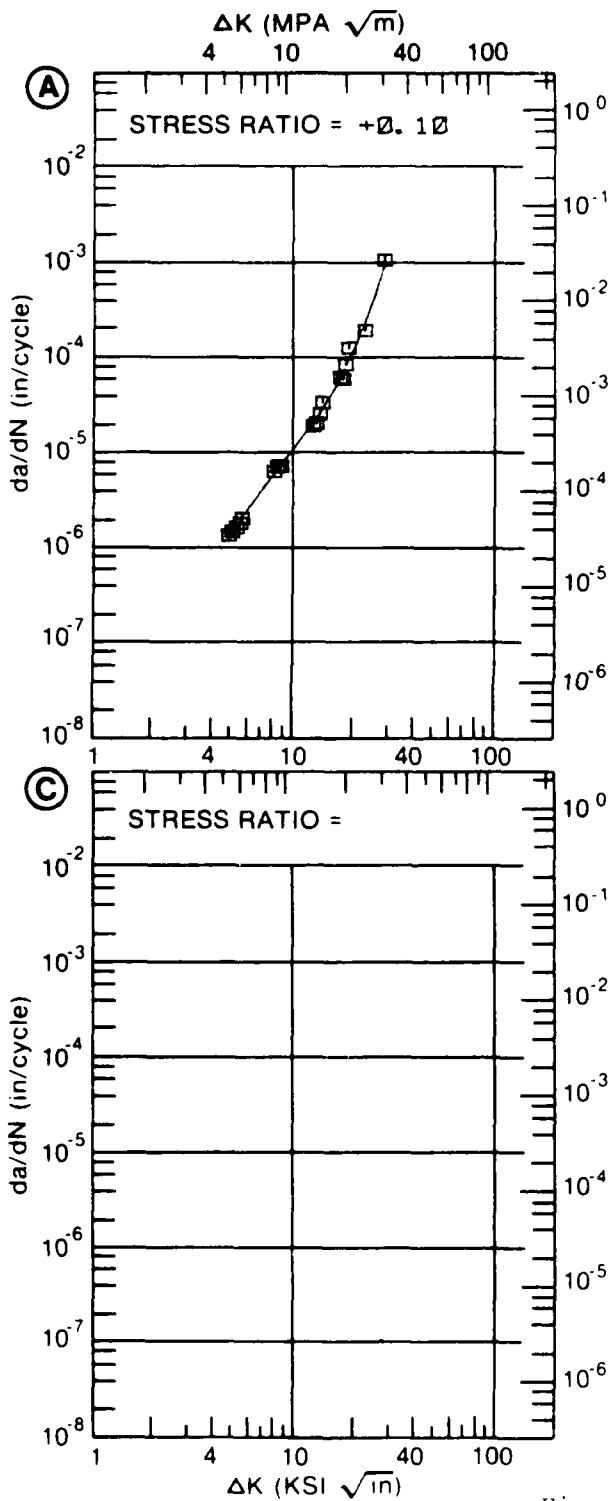


Figure 7.5.3.52

TABLE 7.5.3.53

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.53 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 20.00		F(HZ)= 30.00	
DELTA K MIN	A: 4.52	.487			
	B: 4.77		.335		
	C:				
	D:				
	5.00	.501		.344	
	6.00	1.18		.492	
	7.00			.957	
	8.00			2.30	
	9.00			5.08	
DELTA K MAX	A: 6.88	2.95			
	B: 9.90		5.11		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		13.49		12.28	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25				
	1.25-2.0				
	>2.0				

CONDITION/HT: T851
 FORM: Ø. 75" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: L-S
 STRESS RATIO: +Ø. 1Ø
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: Ø. 759- Ø. 76Ø"
 SPECIMEN WIDTH: 5. ØØ3"
 REFERENCES: 9Ø981

ALUM.
 ALLOY
 2Ø24

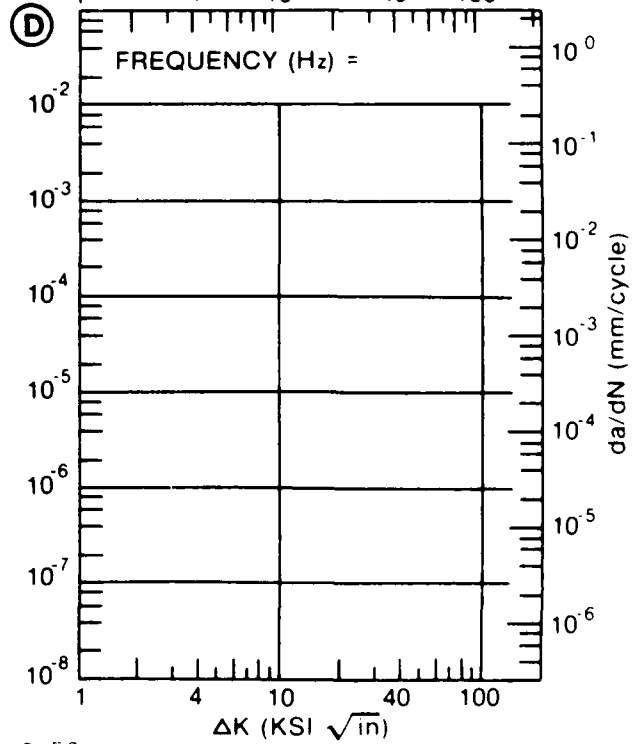
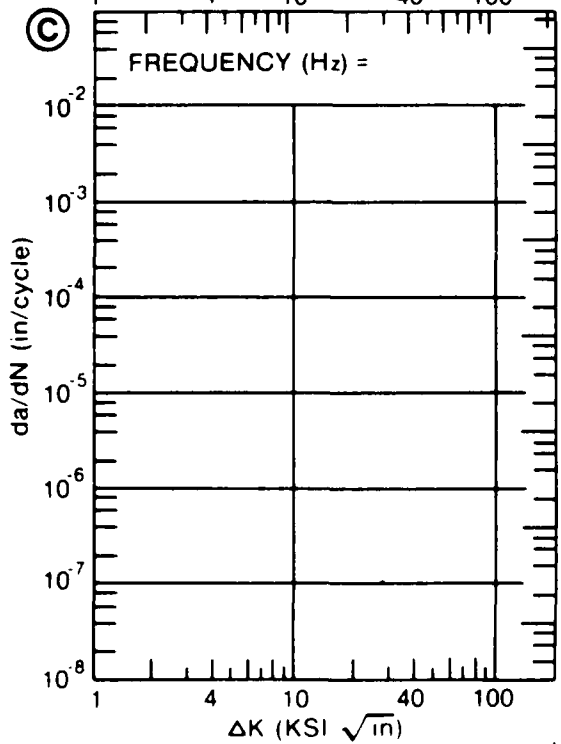
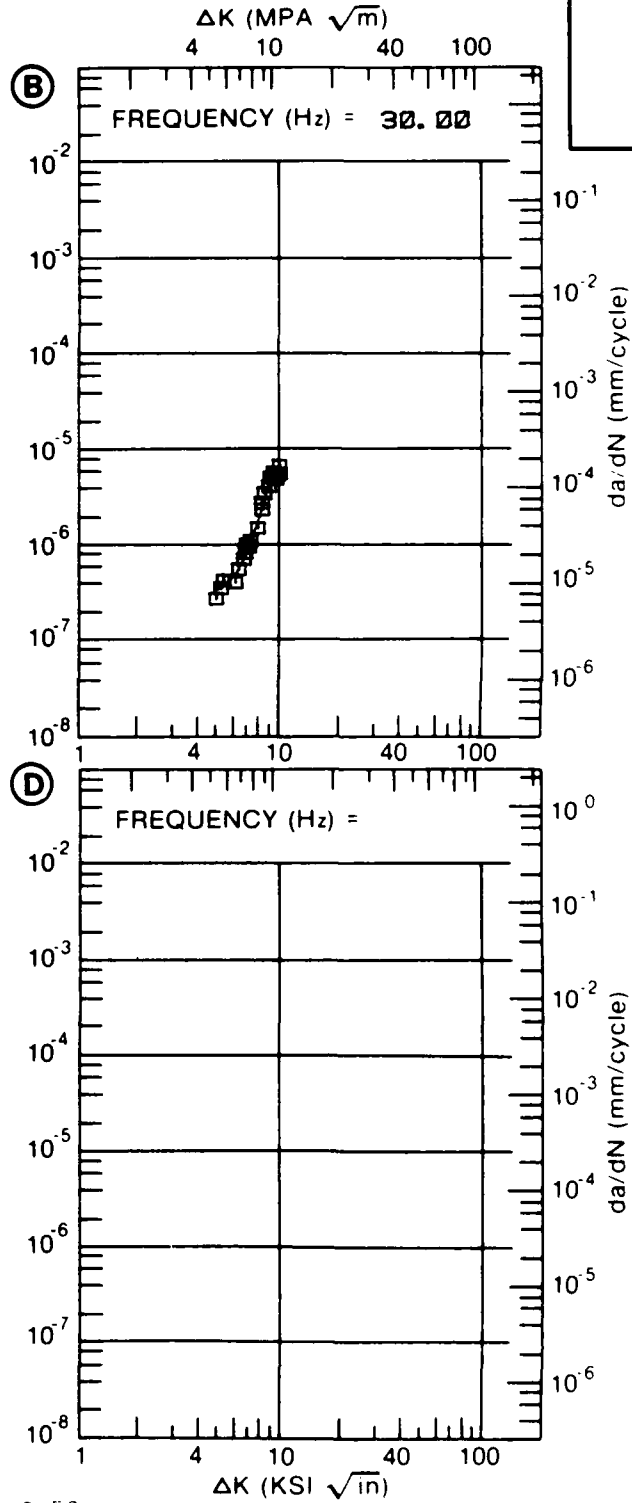
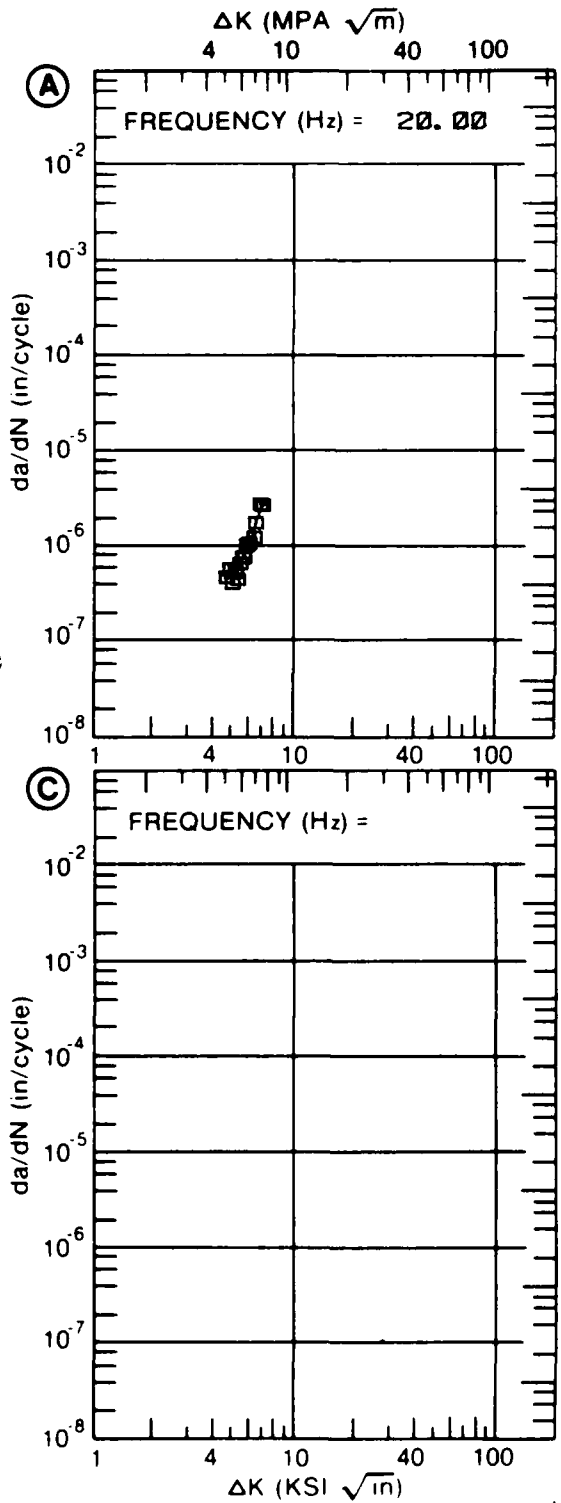


Figure 7.5.3.53

TABLE 7.5.3.54

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.54 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 2024
CONDITION: T851

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	E= R. T. H. H. A.			
DELTA K A: 2.75	.0113			
MIN B:				
C:				
D:				
3.00	.0269			
3.50	.101			
4.00	.261			
5.00	.929			
6.00	2.09			
7.00	3.72			
8.00	5.85			
9.00	8.61			
10.00	12.2			
13.00	32.3			
16.00	85.6			
DELTA K A: 16.67	107.			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 17.12
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 25.00 HZ

YIELD STRENGTH: 67.0 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: NC003

ALUM. ALLOY
2024

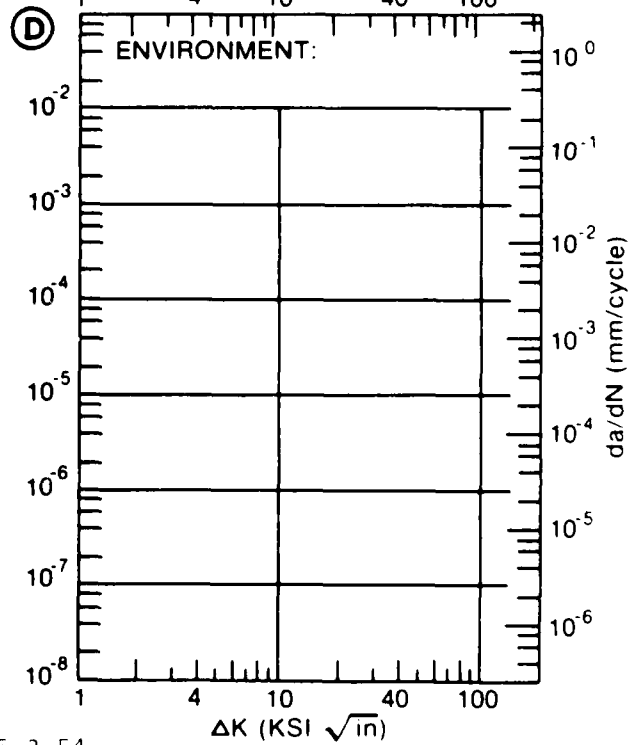
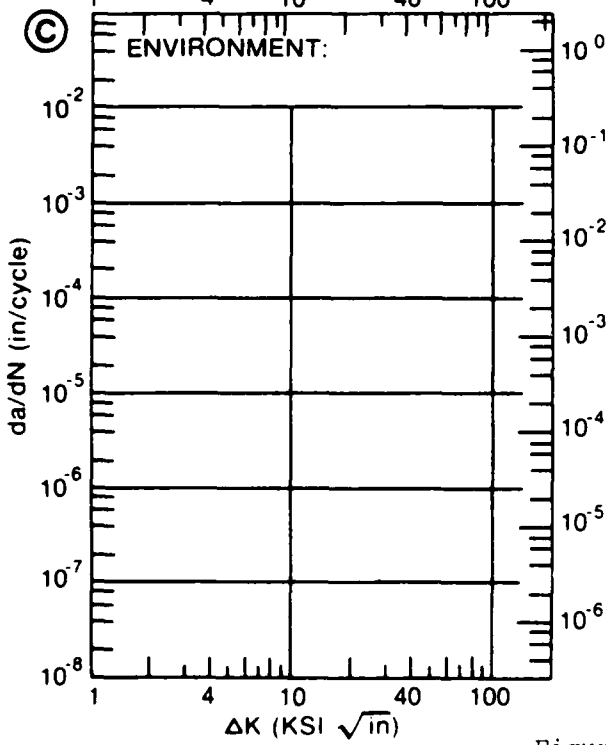
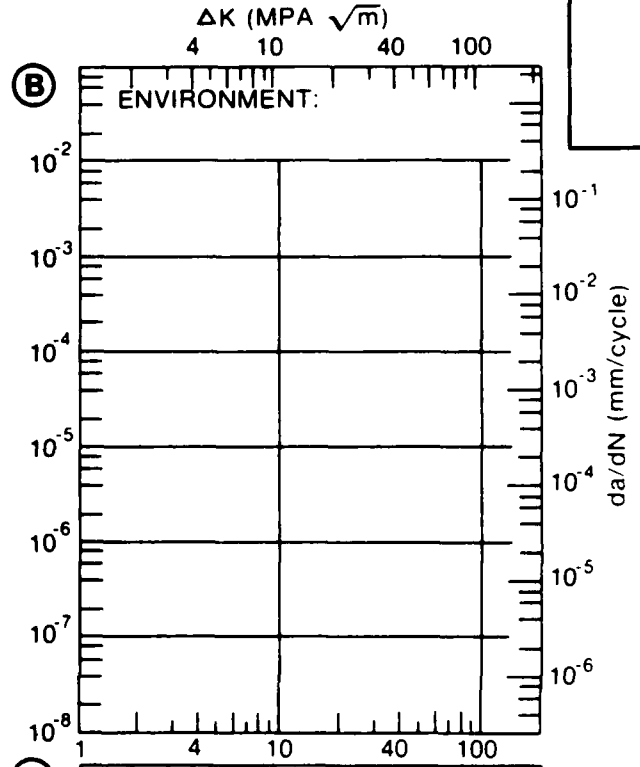
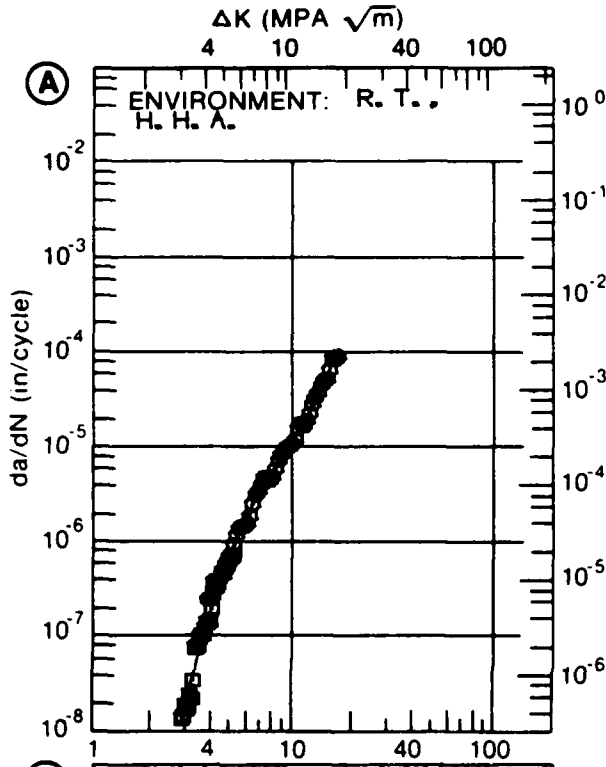


Figure 7.5.3.54

TABLE 7.5.3.55

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.55 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K A:	3.22	.16			
DELTA K B:	1.82		.04		
MIN C:	2				
D:					
	2.00		.0515		
	2.50		.0796		
	3.00		.142		
	3.50	.211	.255		
	4.00	.314	.443		
	5.00	.639	1.13		
	6.00	1.16	2.26		
	7.00	1.89	3.70		
	8.00	2.84	5.10		
	9.00	3.97	6.09		
	10.00	5.24	6.47		
	13.00	9.14			
	16.00	12.0			
DELTA K A:	18.47	13.0			
DELTA K B:	10.31		6.46		
MAX C:					
D:					
ROOT MEAN SQUARE		36.98	35.40		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.758- 0.764"
 SPECIMEN WIDTH: 5.000- 5.005"
 REFERENCES: 90981

ALUM.
ALLOY

2024

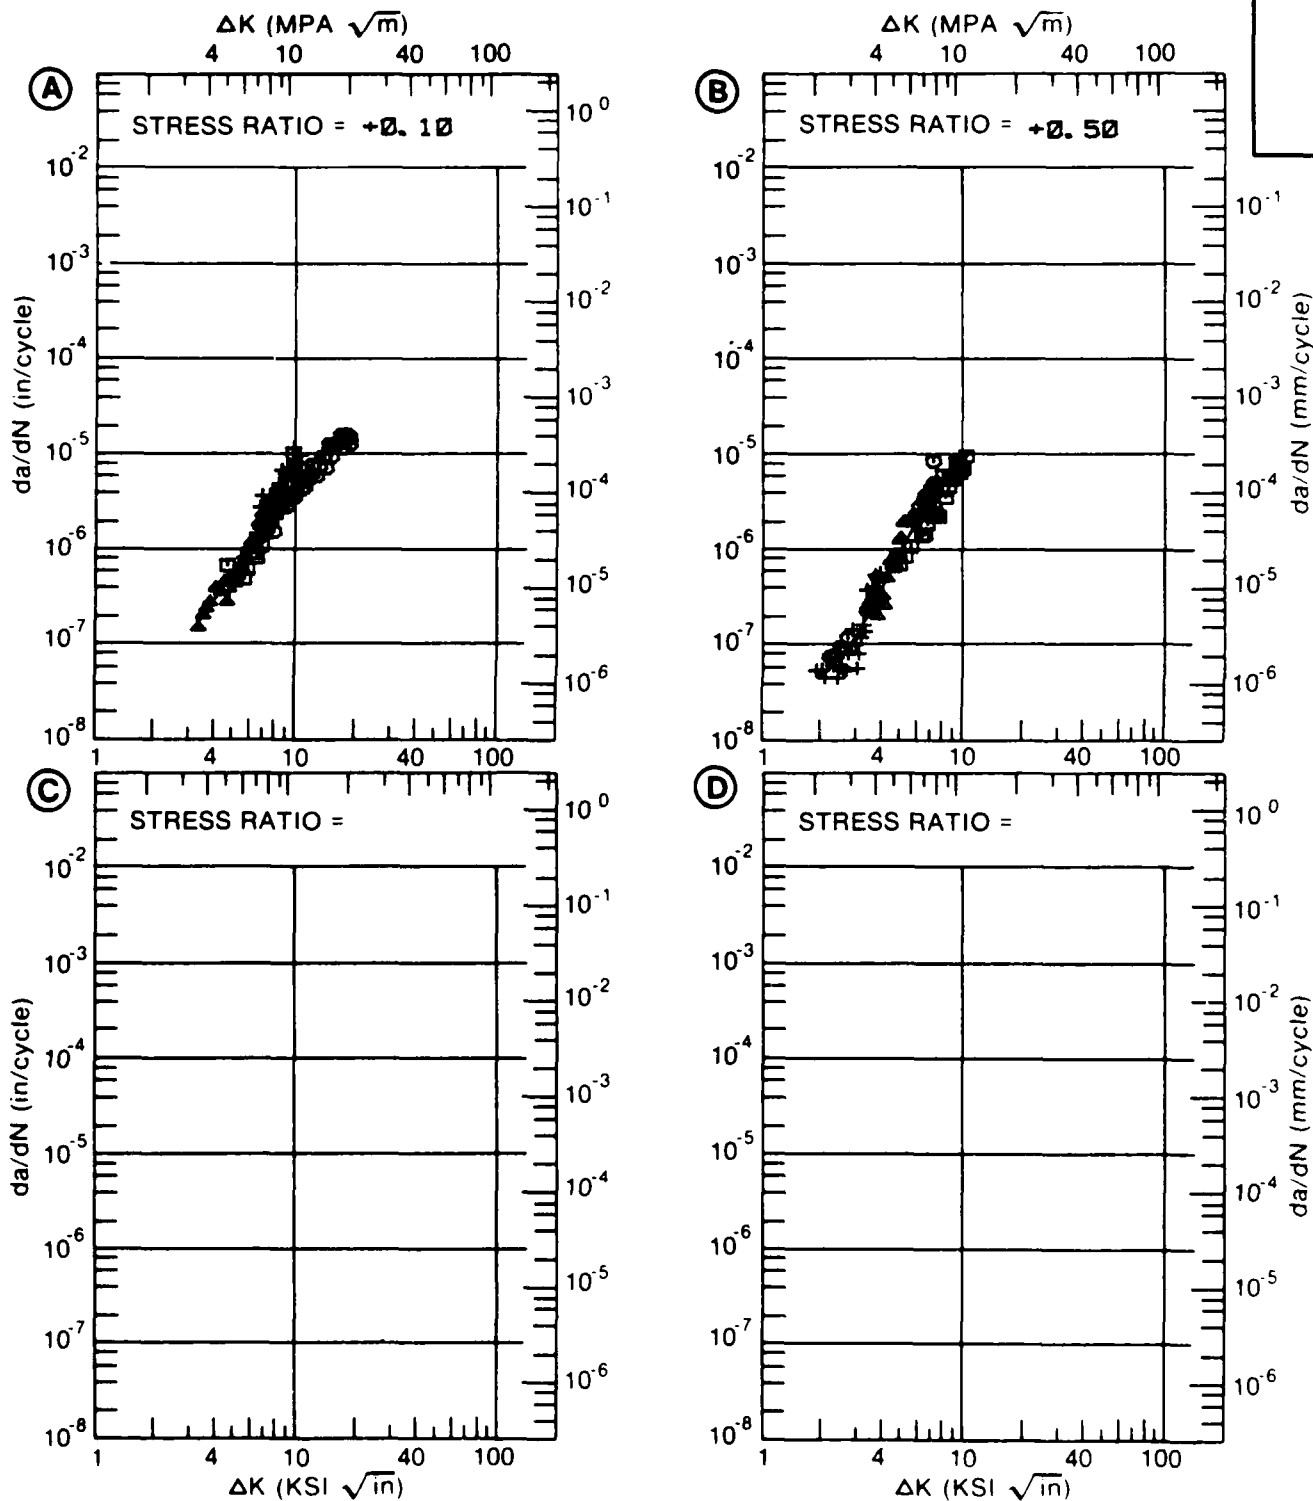


Figure 7.5.3.55

TABLE 7.5.3.56

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.56 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. . H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 50		
DELTA K	A: 11. 66	7. 64			
MIN	B: 4. 25		. 34		
	C:				
	D:				
	5. 00		. 991		
	6. 00		2. 04		
	7. 00		3. 05		
	8. 00		4. 37		
	9. 00		6. 73		
	10. 00		11. 7		
	13. 00	9. 86			
	16. 00	19. 7			
DELTA K	A: 18. 52	52. 3			
MAX	B: 10. 47		16. 0		
	C:				
	D:				
ROOT MEAN SQUARE		19. 13	22. 28		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: T851
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 2.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.759- 0.763"
 SPECIMEN WIDTH: 5.004- 5.006"
 REFERENCES: 90981

ALUM.
 ALLOY

2024

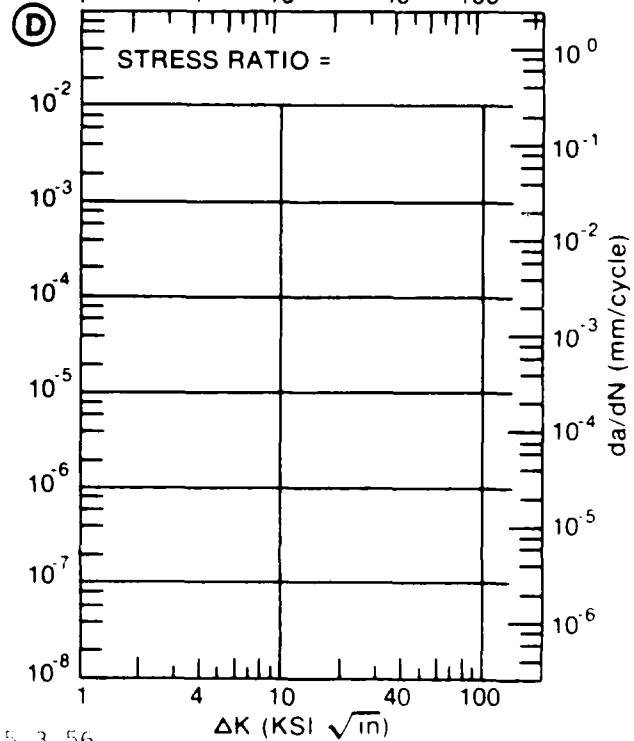
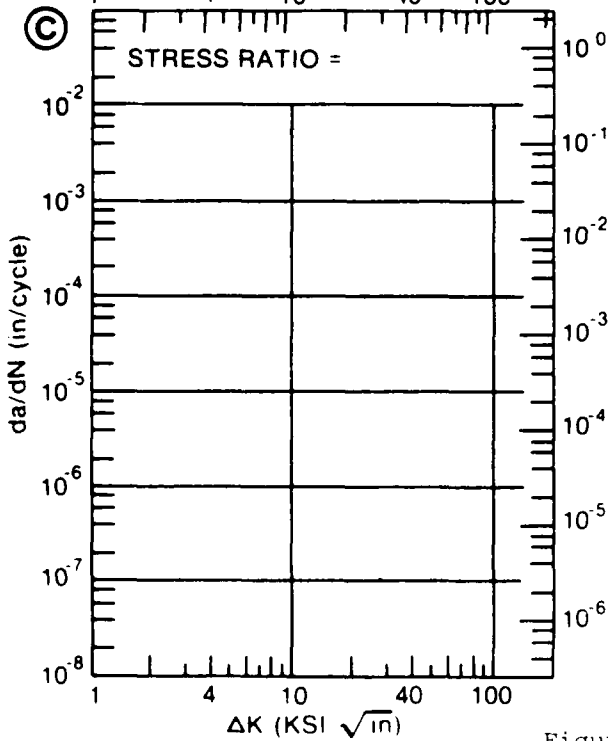
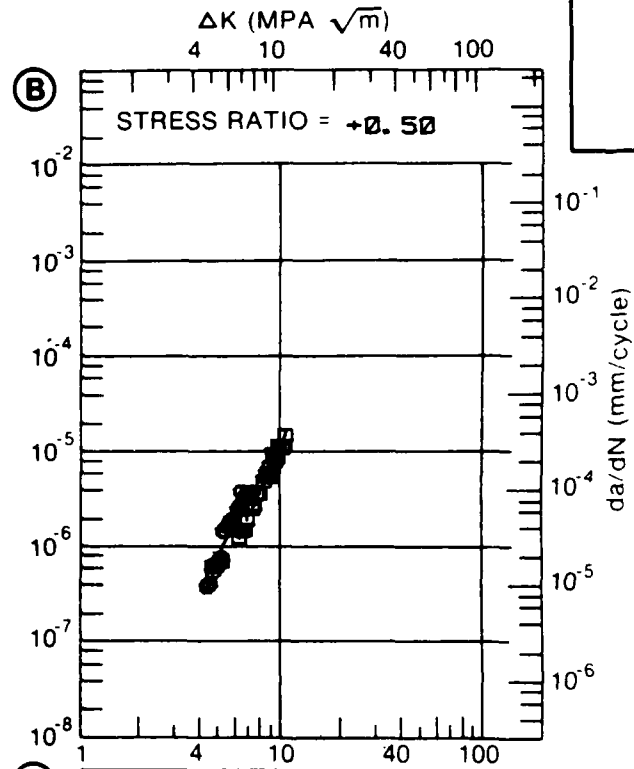
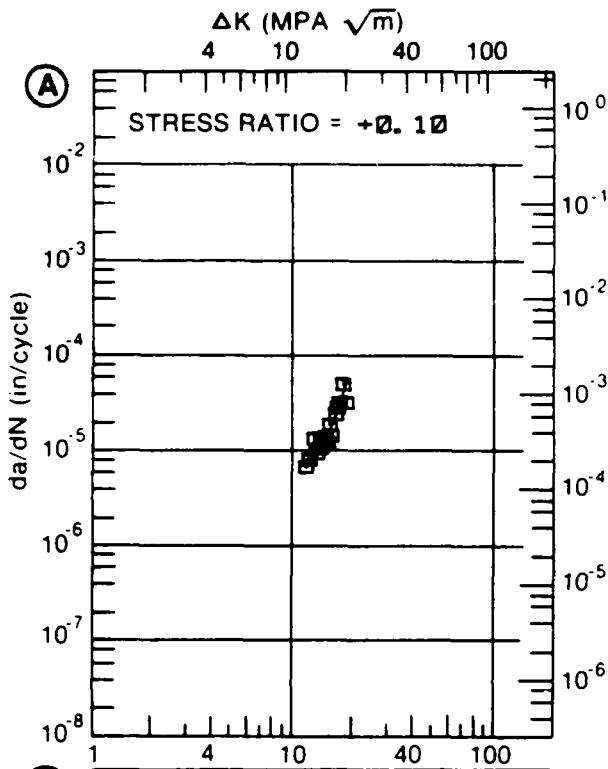


Figure 7.5.3.56

TABLE 7.5.3.57

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.57 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T851
ENVIRONMENT: R. T. , 3.5% NA CL

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K	A: 8.12	4.28			
MIN	B:				
	C:				
	D:				
	9.00	5.11			
	10.00	5.92			
	13.00	10.6			
	16.00	33.0			
DELTA K	A: 17.38	67.8			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 17.89
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: Ø. 76" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: Ø. 763"
 SPECIMEN WIDTH: 5.003"
 REFERENCES: 90981

ALUM. ALLOY
2024

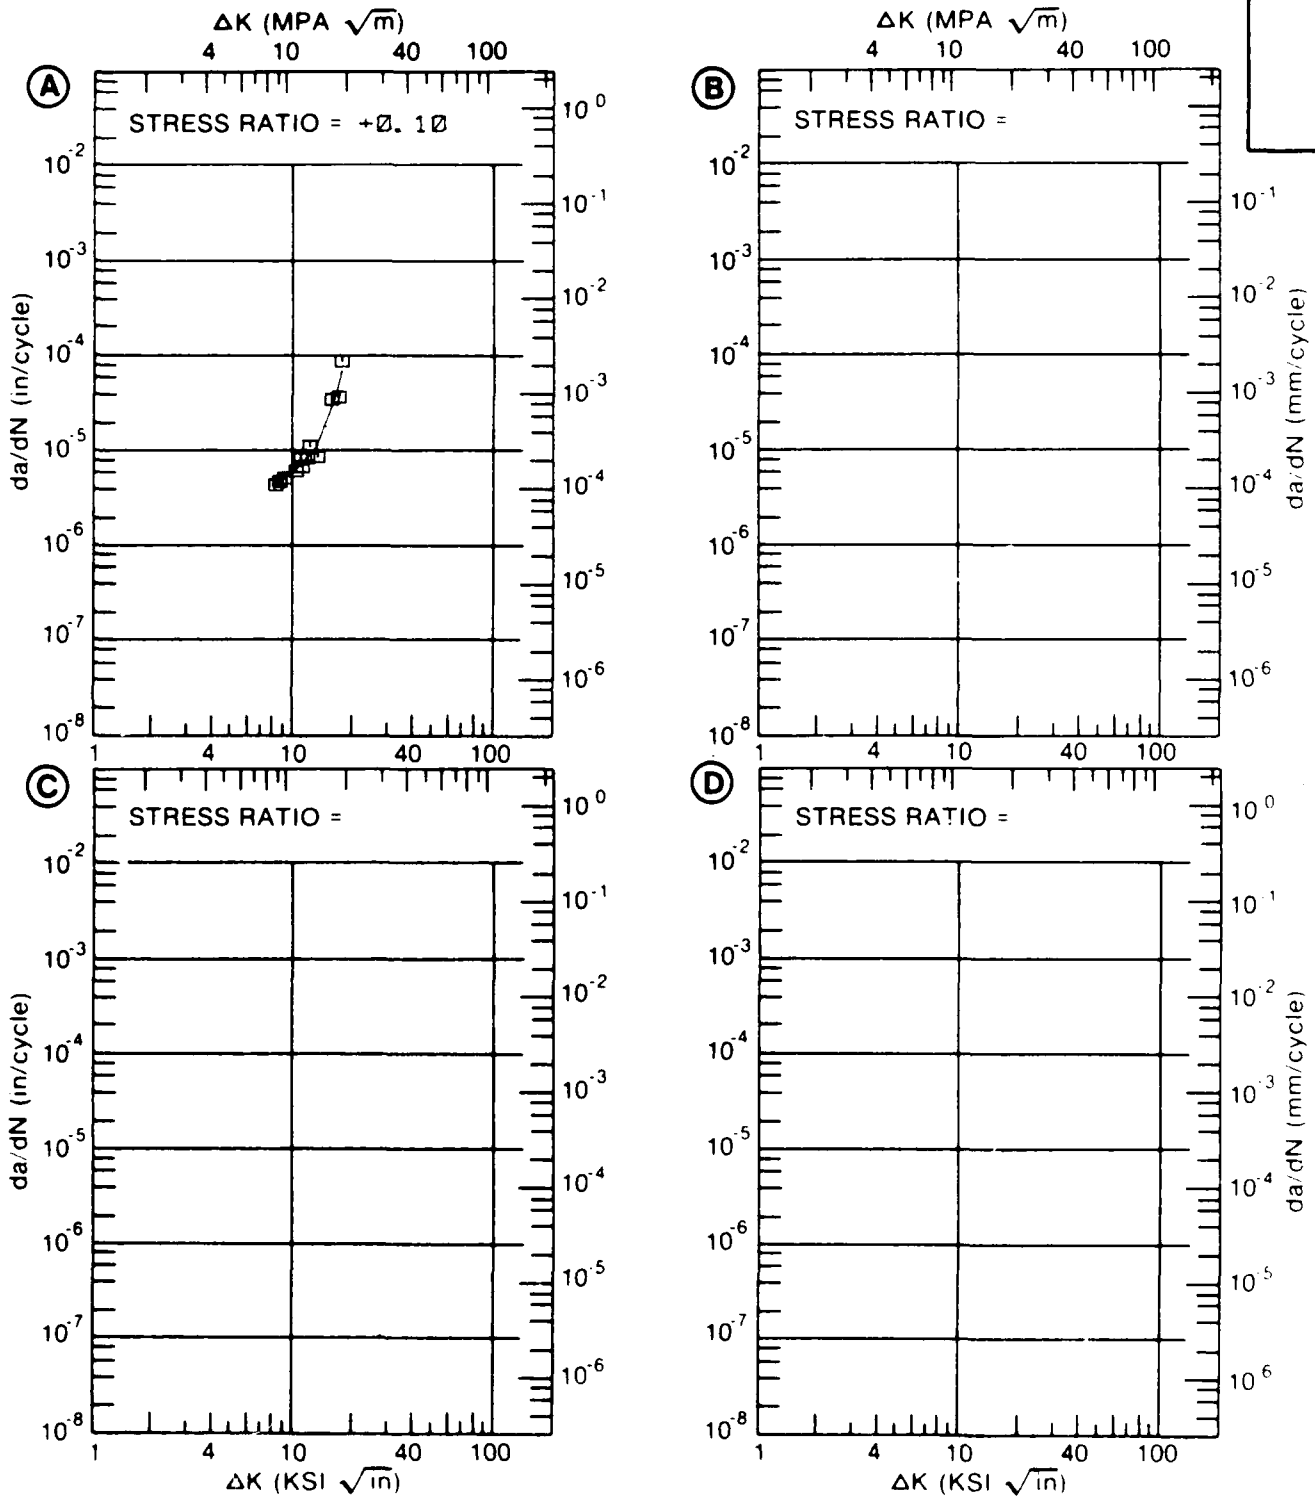


Figure 7.5.3.57

TABLE 7.5.3.58

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.58 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , 3. 5% NaCl					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 50		
DELTA K MIN	A: 4. 82	. 988			
	B: 5. 20		968		
	C:				
	D:				
	5. 00	1. 18			
	6. 00	2. 08	1. 78		
	7. 00	2. 68	3. 18		
	8. 00	3. 23	5. 04		
	9. 00	4. 12	7. 48		
	10. 00	5. 81	10. 7		
	13. 00		28. 3		
	16. 00		72. 8		
	20. 00		265.		
DELTA K MAX	A: 11. 40	11. 5			
	B: 20. 76		340.		
	C:				
	D:				
ROOT MEAN SQUARE		16. 87	21. 52		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: T851
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: PTSF
 ORIENTATION: T-S
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.750- 0.763"
 SPECIMEN WIDTH: 5.000- 5.005"
 REFERENCES: 90981

ALUM. ALLOY
2024

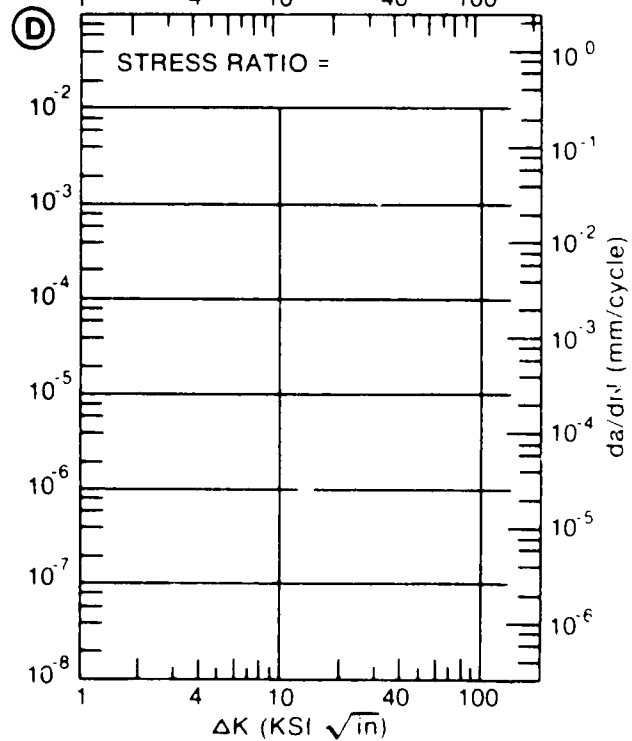
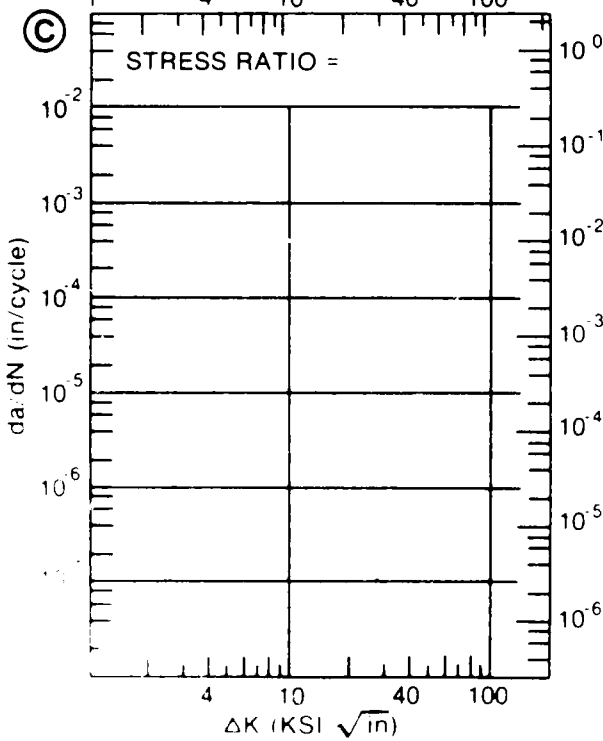
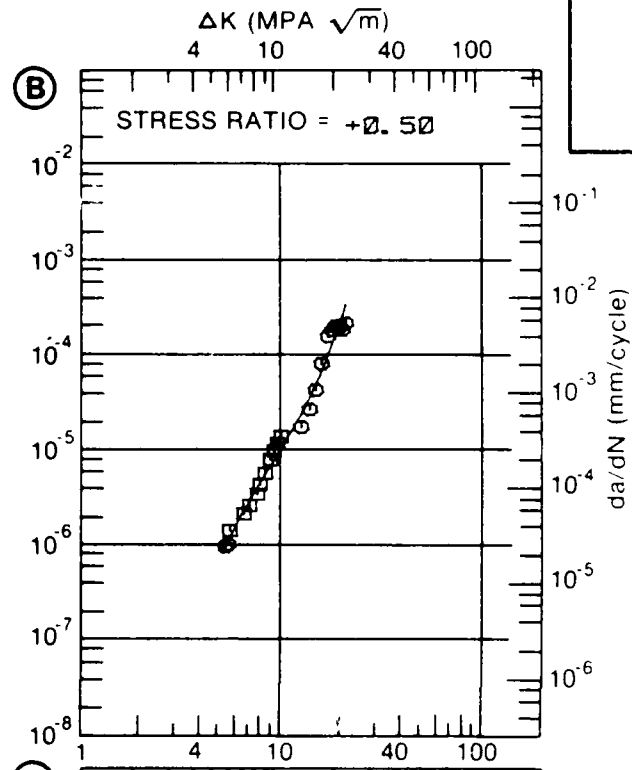
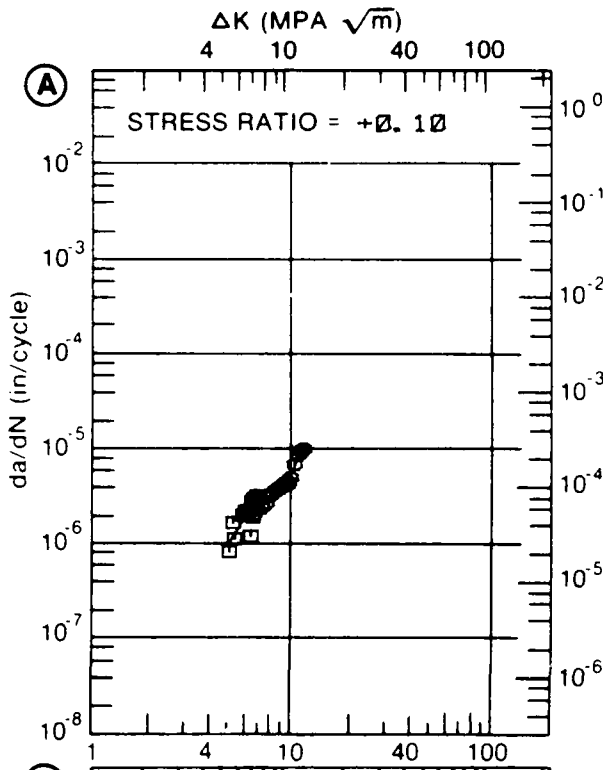


Figure 7.5.3.58

TABLE 7.5.3.59

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.59 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024		
CONDITION: T851				
ENVIRONMENT: R. T. , H. H. A.				
DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	R=+0.10			
A: 4.01	.339			
DELTA K B:				
MIN C:				
D:				
5.00	.509			
6.00	1.26			
7.00	2.58			
8.00	4.36			
9.00	6.54			
10.00	9.04			
13.00	18.0			
16.00	29.5			
A: 18.82	57.7			
DELTA K B:				
MAX C:				
D:				
ROOT MEAN SQUARE		7.74		
PERCENT ERROR				
LIFE	0.0-0.5			
PREDICTION	0.5-0.8			
RATIO	0.8-1.25	1		
SUMMARY	1.25-2.0			
(NP/NA)	>2.0			

CONDITION/HT: T851
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 68.6 KSI
 ULT. STRENGTH: 73.0 KSI
 SPECIMEN THK: 0.761"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

ALUM.
ALLOY

2024

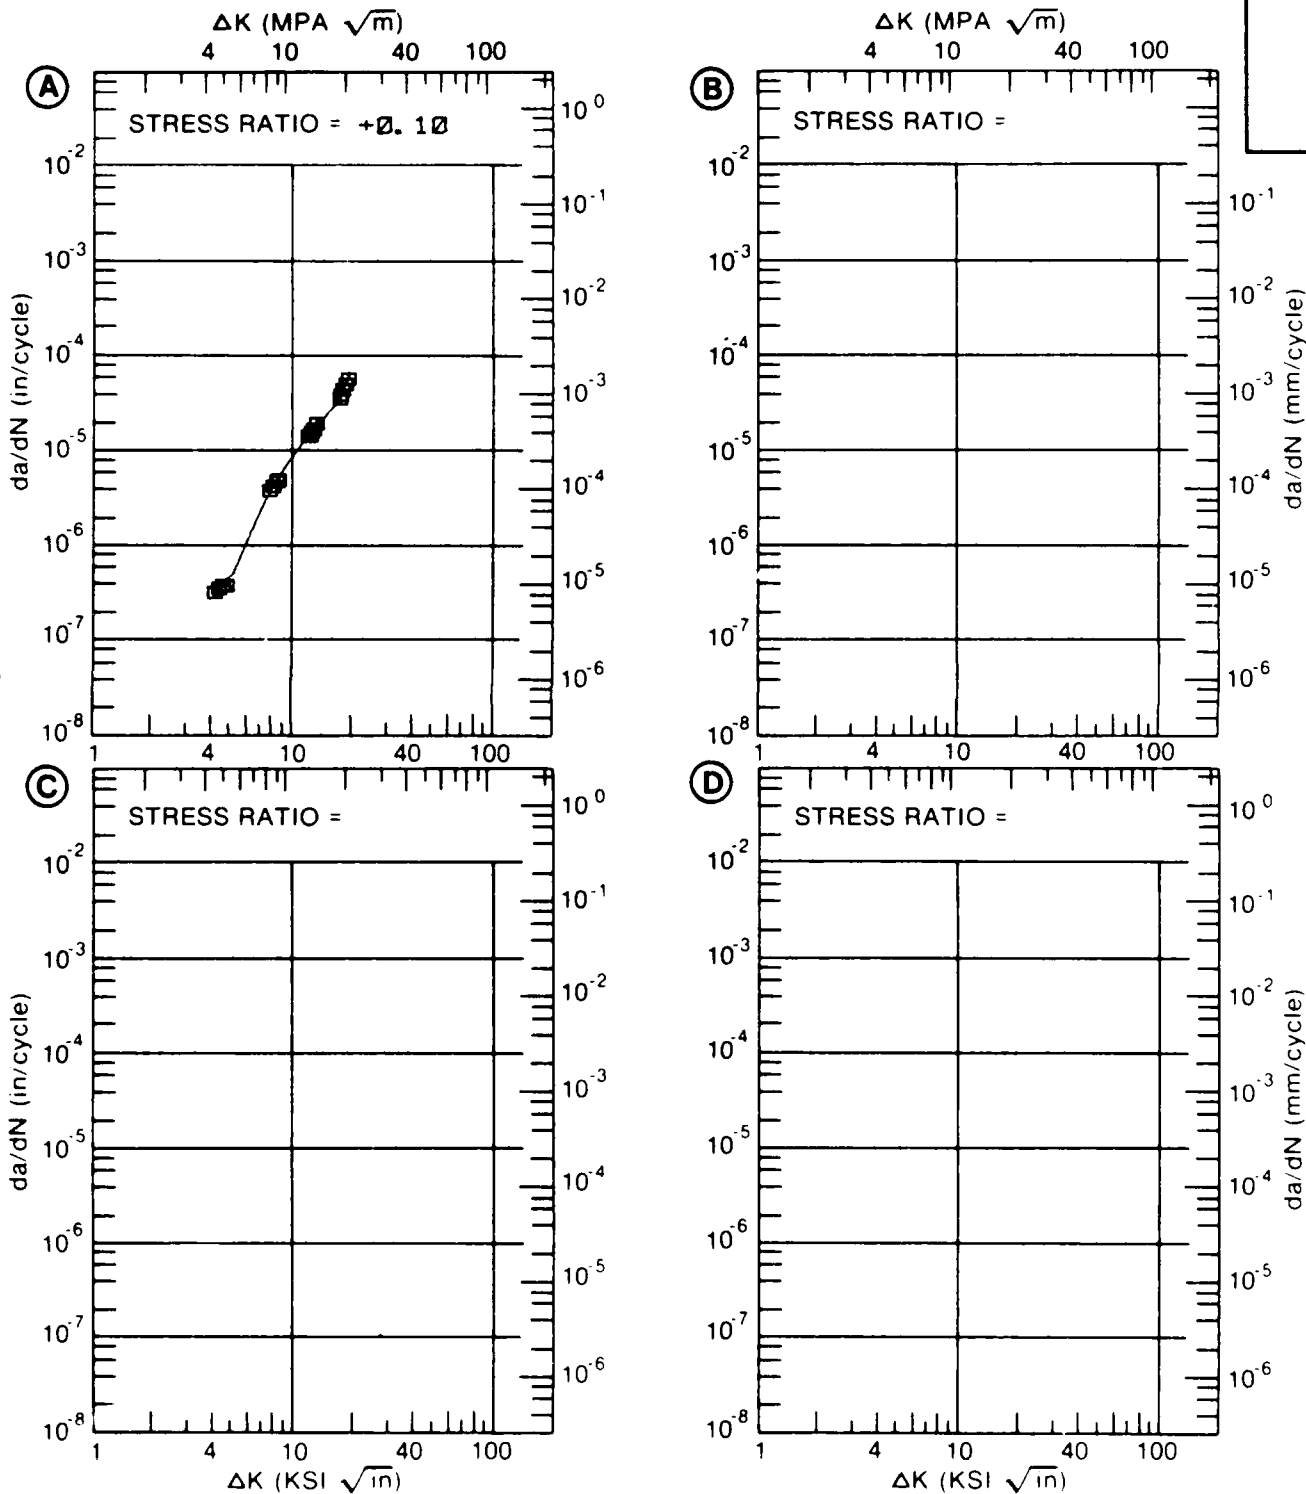


Figure 7.5.3.59

TABLE 7.5.3.60

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.60 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.	E= R. T. 3. 5% NA CL		
DELTA K MIN	A:	11. 66	7. 64		
	B:				
	C:				
	D:				
		13. 00	9. 86		
		16. 00	19. 7		
DELTA K MAX	A:	18. 52	52. 3		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		19. 13	0. 00		
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: T851
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: P-SF
 ORIENTATION: T-S
 STRESS RATIO: +0.10
 FREQUENCY: 2.00 HZ

YIELD STRENGTH: 70.1 KSI
 ULT. STRENGTH: 73.5 KSI
 SPECIMEN THK: 0.759- 0.763"
 SPECIMEN WIDTH: 5.003- 5.004"
 REFERENCES: 90981

ALUM. ALLOY
2024

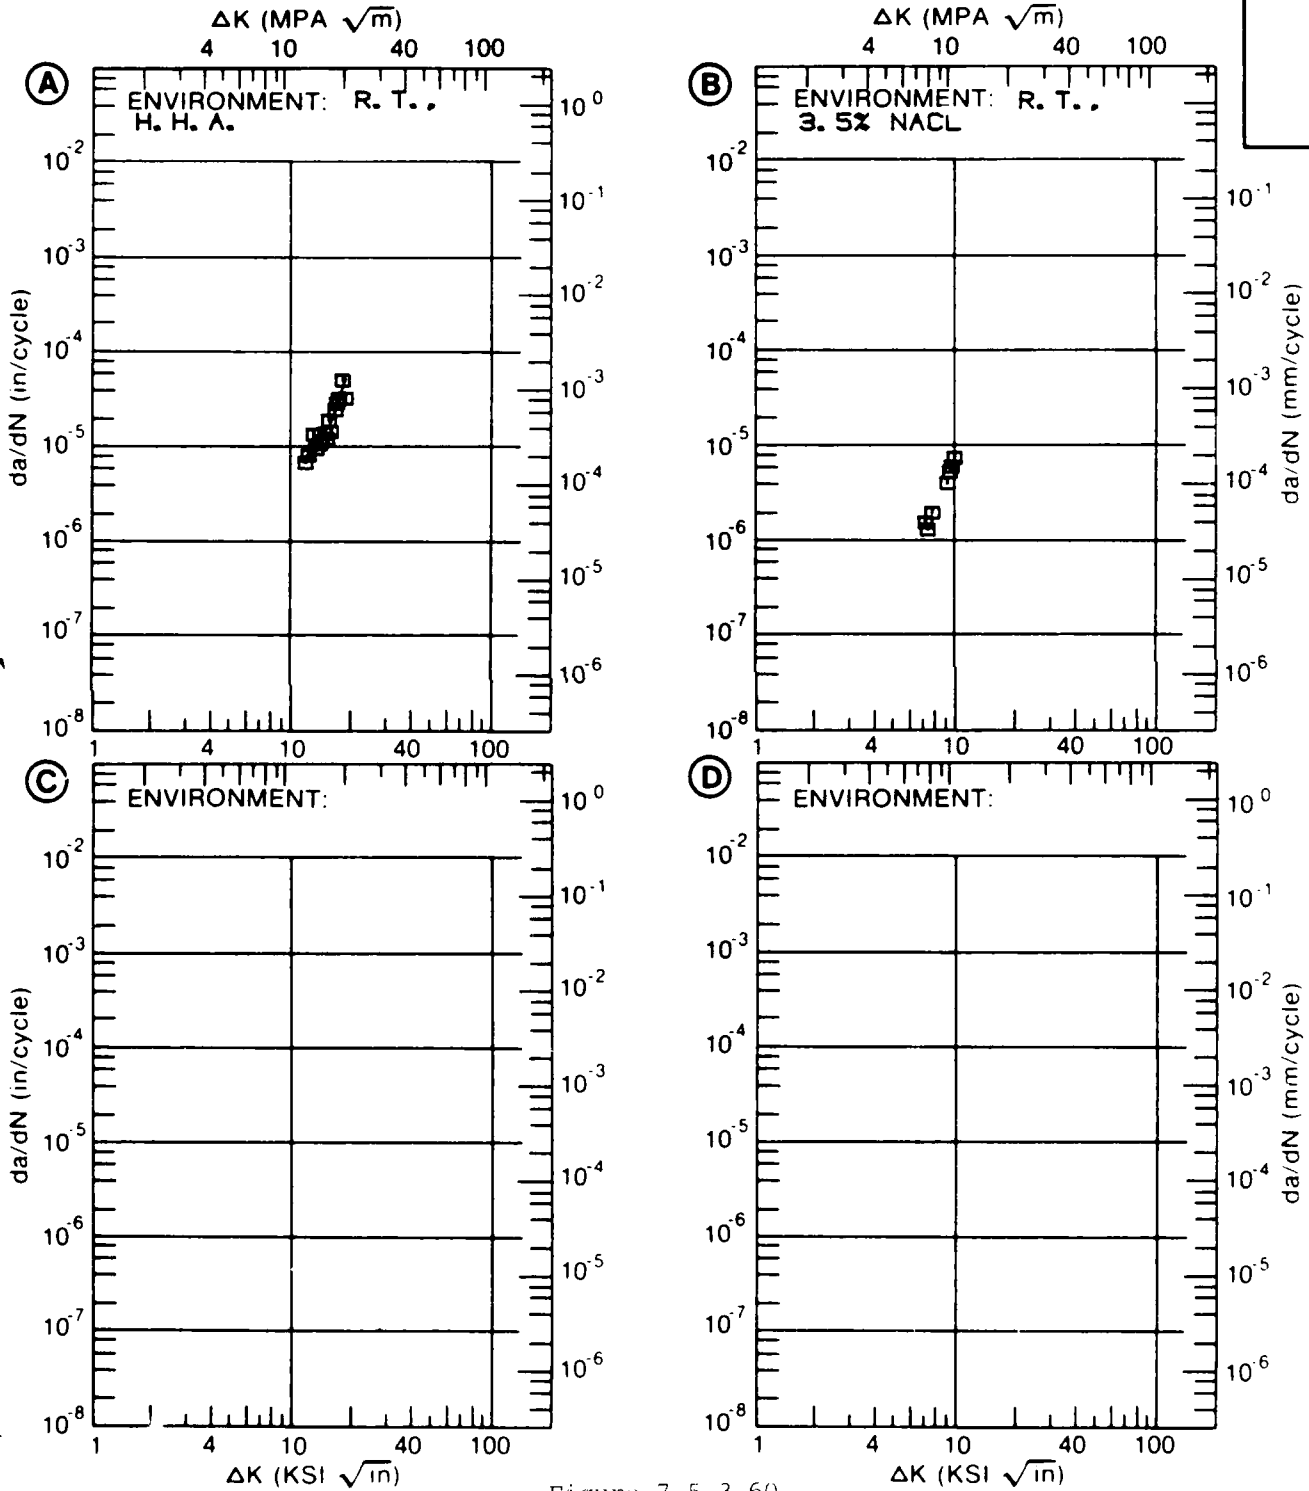


Figure 7.5.3.60

TABLE 7.5.3.61

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.61 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , 3.5% NaCl					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K MIN	A: 3.33	.193			
	B: 2.12		.119		
	C:				
	D:				
	2.50		.215		
	3.00		.406		
	3.50	.236	.689		
	4.00	.399	1.08		
	5.00	.915	2.28		
	6.00	1.75	4.17		
	7.00	2.98	6.93		
	8.00	4.68	10.7		
	9.00	6.96	15.8		
	10.00	9.93	22.4		
	13.00	24.3			
	16.00	50.5			
DELTA K MAX	A: 16.68	58.8			
	B: 11.10		31.7		
	C:				
	D:				
ROOT MEAN SQUARE		22.26	18.87		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	1	1		
	1.25-2.0				
	>2.0				

CONDITION/HT: T851
 FORM: 0.75" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 20.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 68.6 KSI
 ULT. STRENGTH: 73.0 KSI
 SPECIMEN THK: 0.760"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 90981

ALUM.
ALLOY

2024

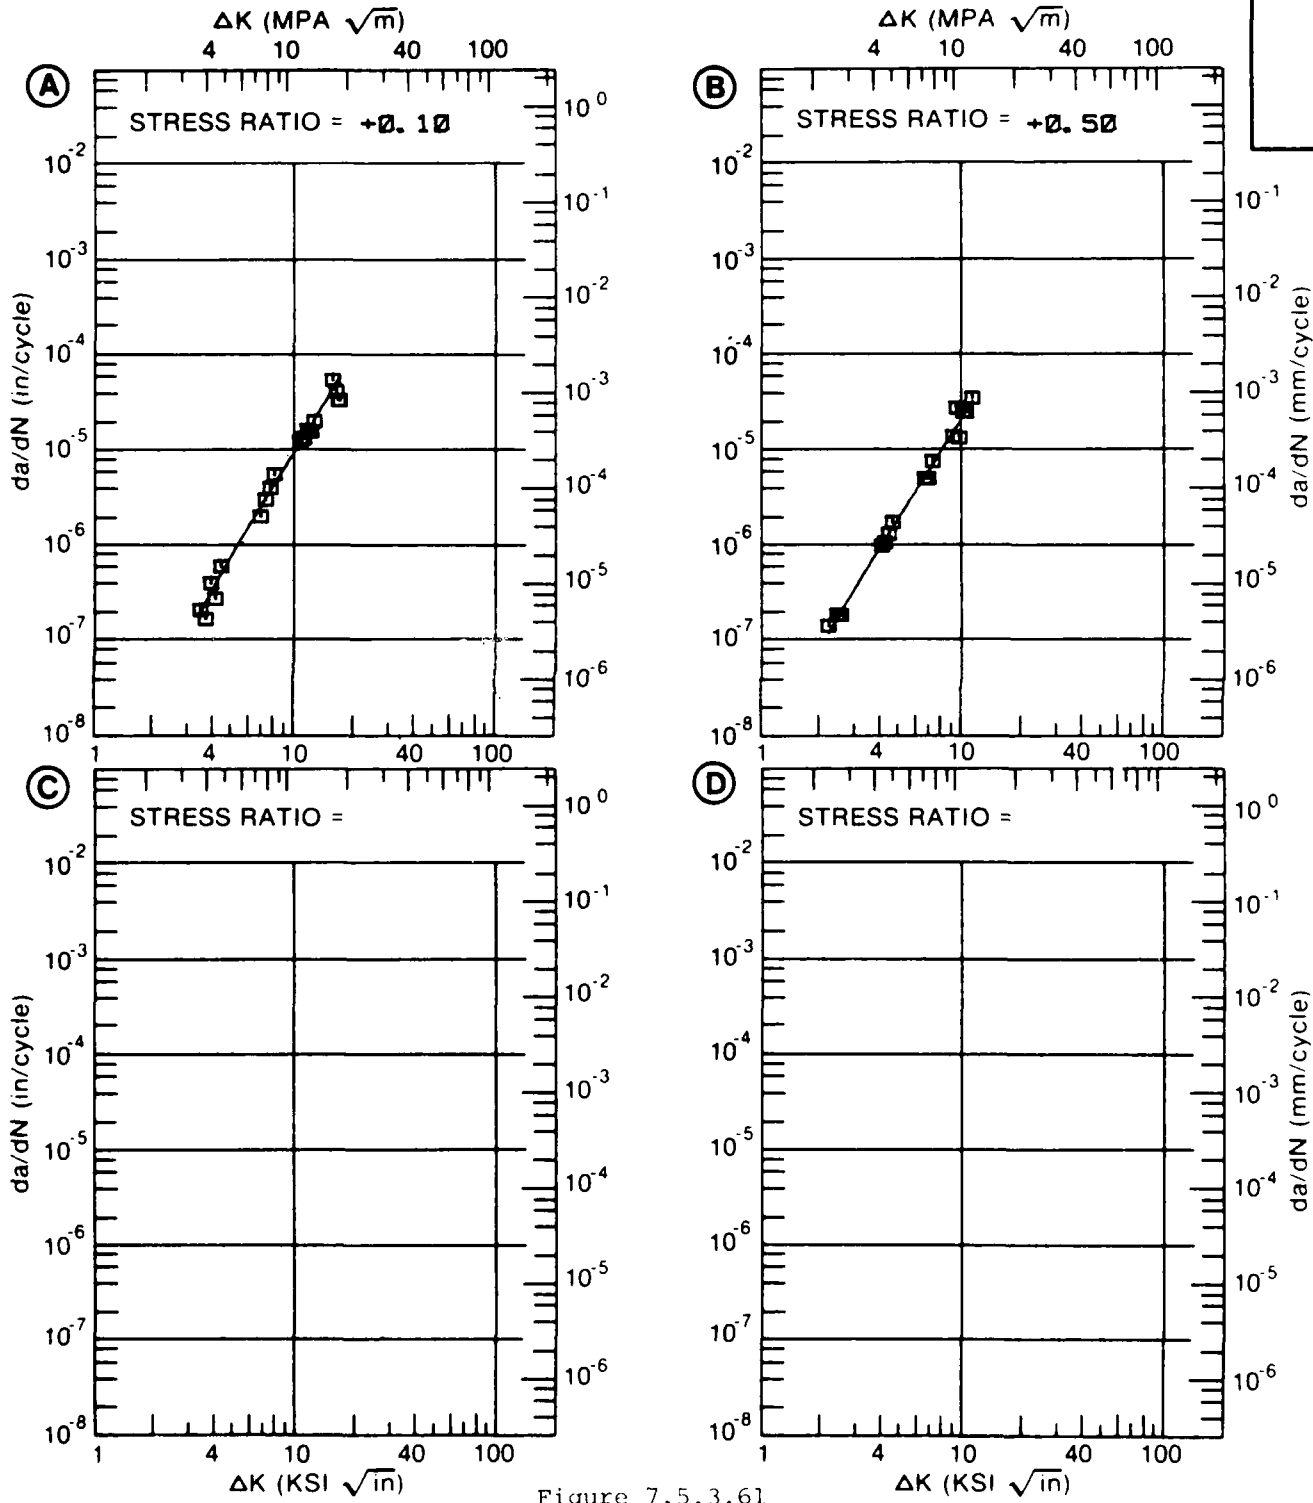


Figure 7.5.3.61

TABLE 7.5.3.62

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.62 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024				
CONDITION: T851				
ENVIRONMENT: R. T. , DRY AIR				
DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	R=+0.20	R=+0.40		
DELTA K A: MIN B: C: D:				
200.00				
DELTA K A: MAX B: C: D:				
ROOT MEAN SQUARE	0.00	0.00		
PERCENT ERROR				
LIFE	0.0-0.5			
PREDICTION	0.5-0.8			
RATIO	0.8-1.25			
SUMMARY	1.25-2.0			
(NP/NA)	>2.0			

CONDITION/HT: T851
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: L-T
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., DRY AIR

YIELD STRENGTH: 64.0 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 5.500"
 REFERENCES: 84360

ALUM. ALLOY
2024

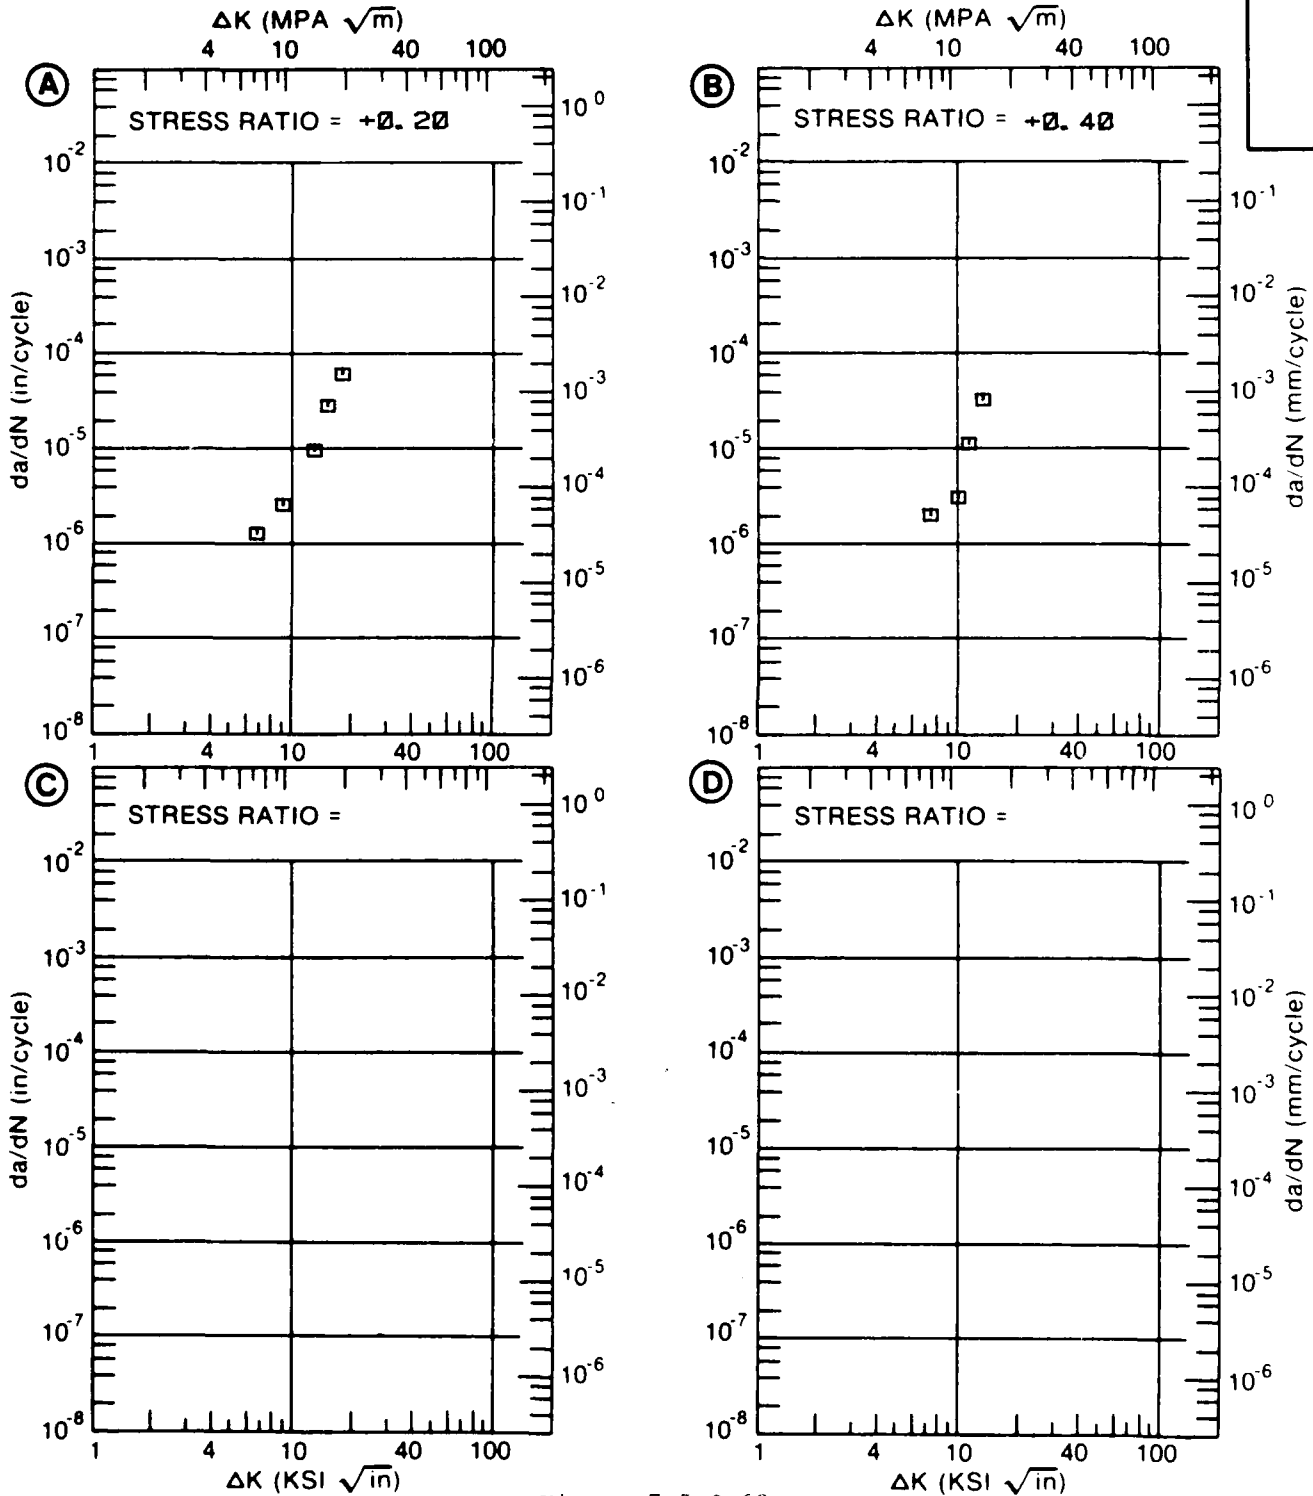


Figure 7.5.3.62

TABLE 7.5.3.63

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.63 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. LAB AIR	E= R. T. JP-4 FUEL	
DELTA K	A:				
MIN	B: 6.40		1.10		
	C: 6.66			.95	
	D:				
	7.00		1.41	1.19	
	8.00		2.04	2.14	
	9.00		2.86	3.50	
	10.00		3.92	5.36	
	13.00		9.28	14.4	
	16.00		20.6	29.3	
	20.00		57.0	58.8	
	25.00		192.	109.	
DELTA K	A:				
MAX	B: 25.87		236.		
	C: 29.26			162.	
	D:				
ROOT MEAN SQUARE		0.00	78.83	32.26	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT. T851
 FORM 2.00- 3.00" TH PLATE
 SPECIMEN TYPE DCB
 ORIENTATION L-T
 STRESS RATIO +0.02
 FREQUENCY 1.00- 10.00 HZ

YIELD STRENGTH: 59.0- 64.0 KSI
 ULT. STRENGTH: 66.0- 71.0 KSI
 SPECIMEN THK: 0.750- 1.000"
 SPECIMEN WIDTH: 5.500"
 REFERENCES: 84360

ALUM.
 ALLOY

2024

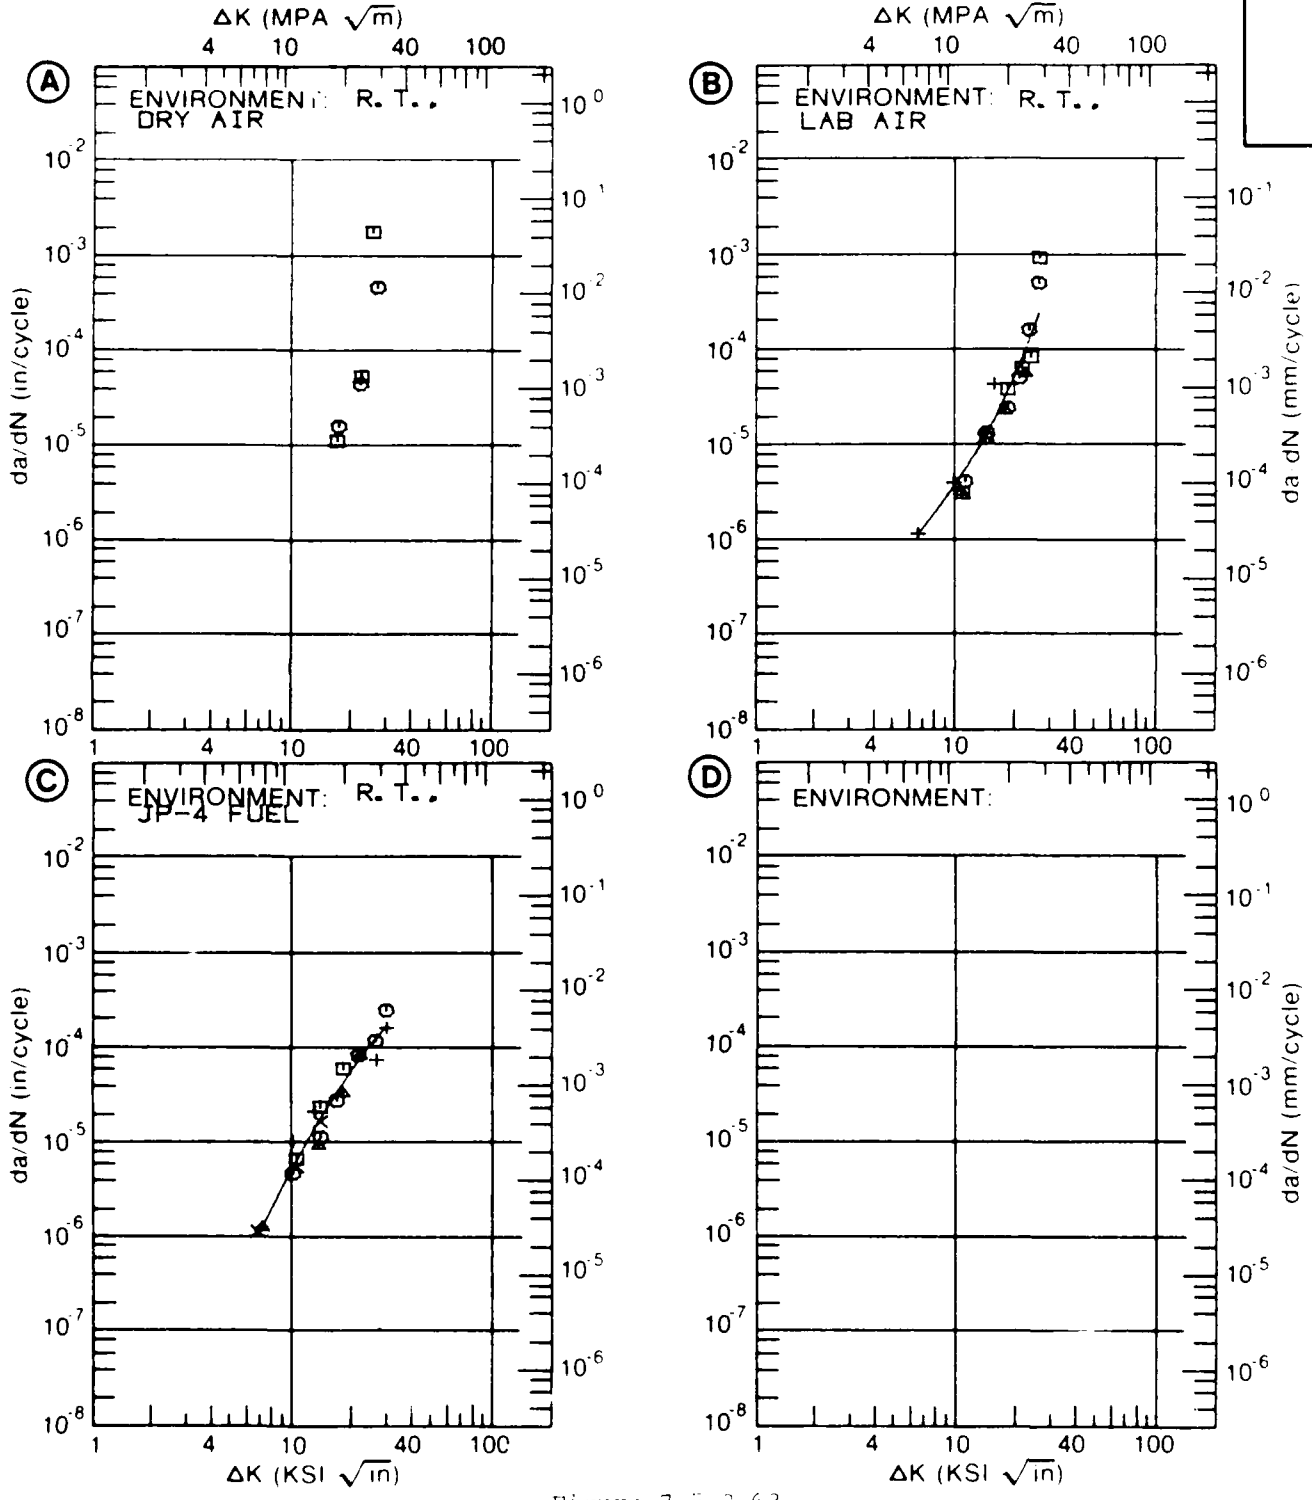


Figure 7.5.3.63

TABLE 7.5.3.64

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.64 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. 3. 5% NACL	E= R. T. SIMULATED FUEL		
DELTA K MIN	A: 9. 58	6. 74			
	B: 9. 62		5. 14		
	C:				
	D:				
	10. 00	7. 28	6. 23		
	13. 00	14. 8	16. 7		
	16. 00	31. 5	34. 4		
	20. 00	74. 2			
DELTA K MAX	A: 24. 72	156.			
	B: 19. 61		97. 2		
	C:				
	D:				
ROOT MEAN SQUARE		37. 42	22. 28		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0. 0-0. 5 0. 5-0. 8 0. 8-1. 25 1. 25-2. 0 >2. 0				

CONDITION/HT: T851
 FORM: 2.00- 3.00" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY: 1.00- 10.00 HZ

YIELD STRENGTH: 59.0- 64.0 KSI
 ULT. STRENGTH: 66.0- 71.0 KSI
 SPECIMEN THK: 0.625- 0.875"
 SPECIMEN WIDTH: 5.500"
 REFERENCES: 84360

ALUM.
 ALLOY

2024

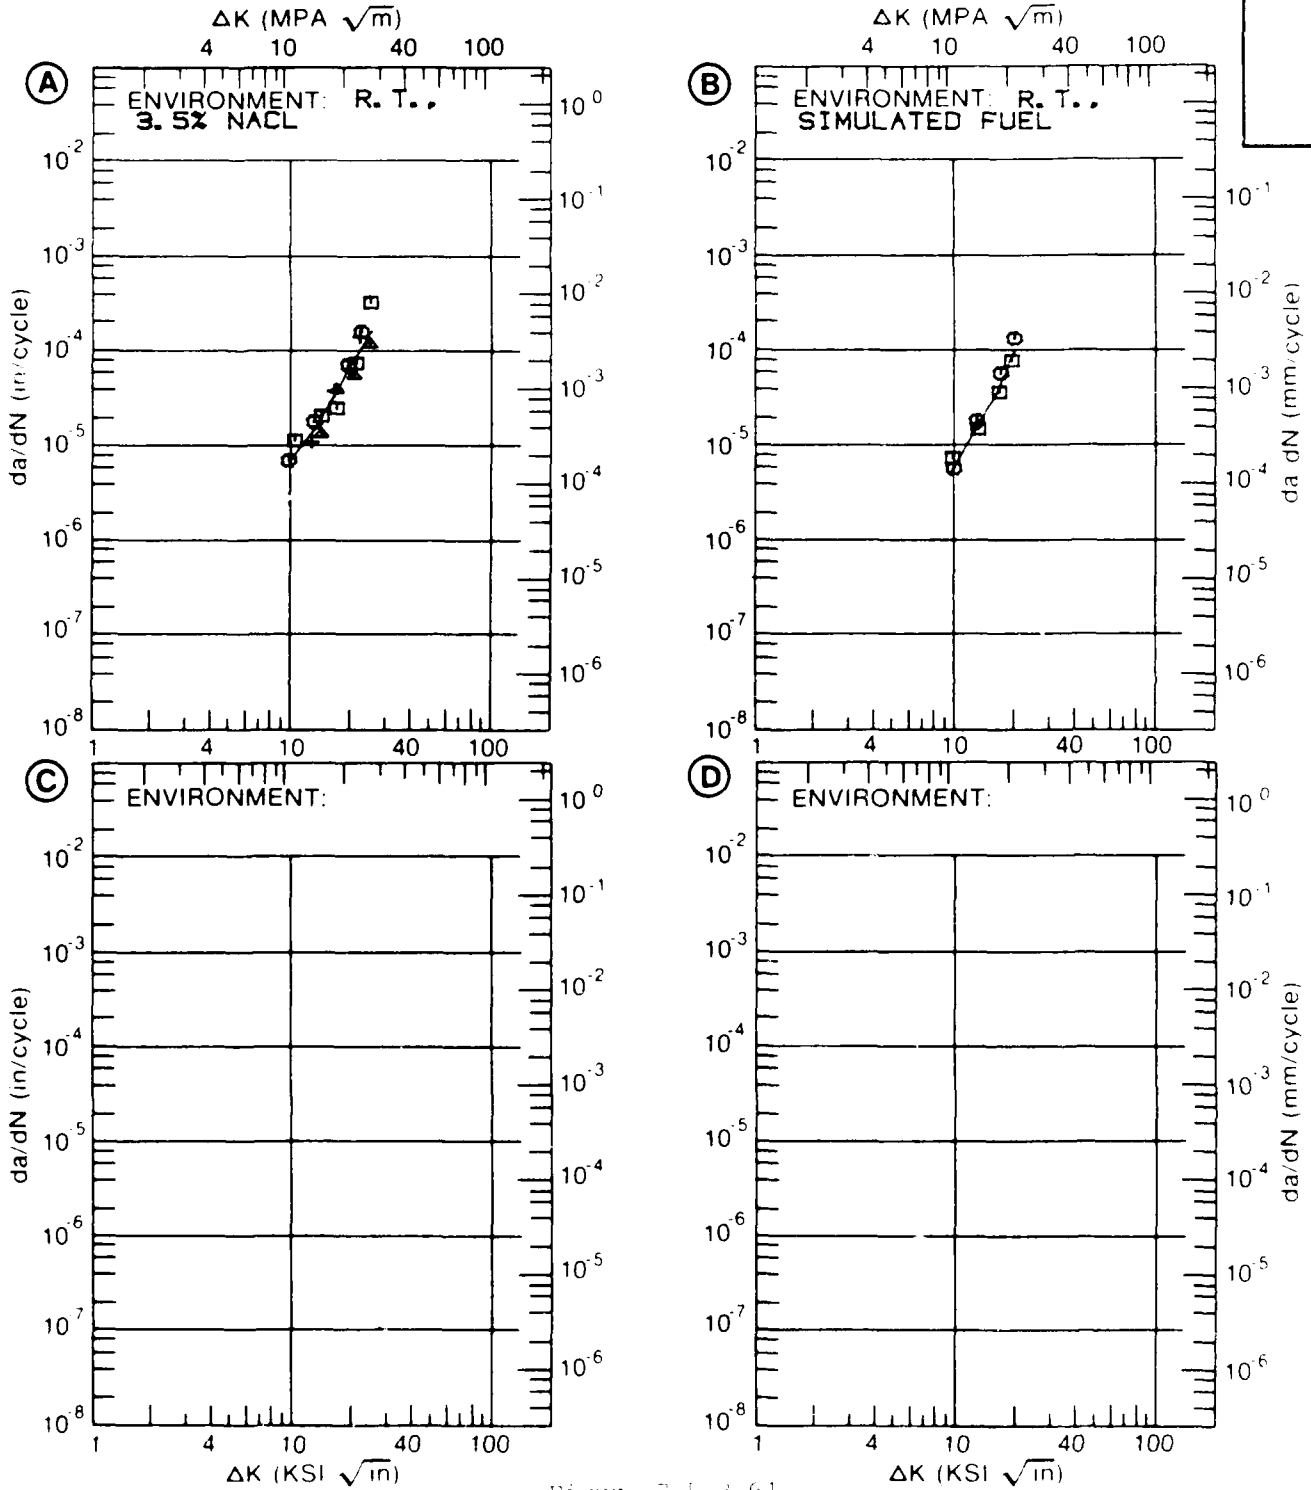


Figure 7.5.3.64

TABLE 7.5.3.65

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.65 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 6.45	.716			
	B:				
	C:				
	D:				
	7.00	2.06			
	8.00	4.10			
	9.00	6.40			
	10.00	8.93			
	13.00	22.1			
	16.00	74.3			
DELTA K MAX	A: 16.92	140.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		17.92			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0	2			
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 51.0- 66.0 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 5.990- 6.010"
 REFERENCES: 88579

ALUM. ALLOY
2024

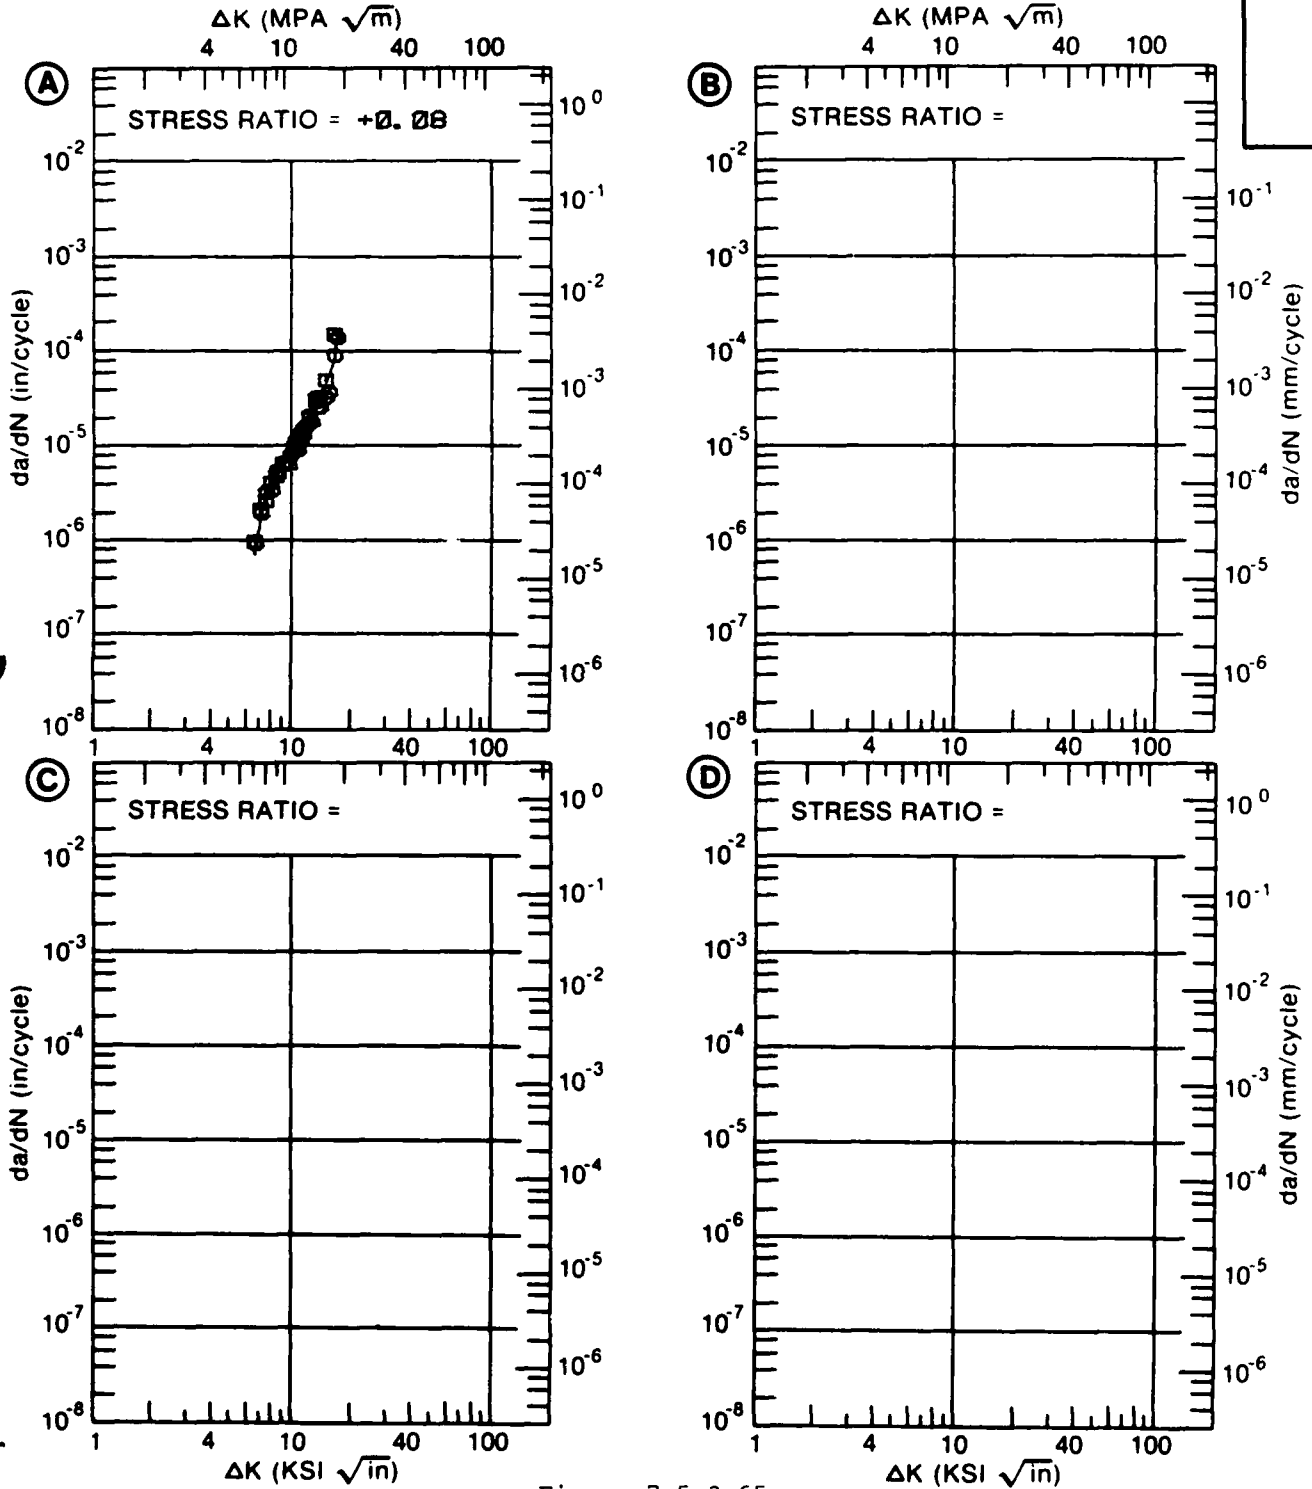


Figure 7.5.3.65

TABLE 7.5.3.66

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.66 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 7.09	1.36			
	B:				
	C:				
	D:				
	8.00	2.39			
	9.00	3.81			
	10.00	5.52			
	13.00	12.5			
	16.00	24.4			
DELTA K MAX	A: 19.44	52.0			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		5.86			
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1			

CONDITION/HT: T851
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 66.0 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 0.494"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837

ALUM. ALLOY
2024

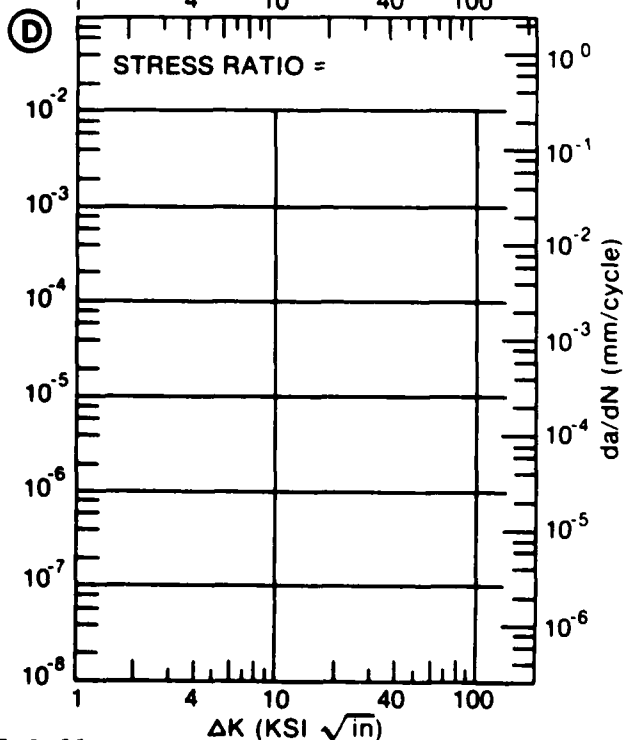
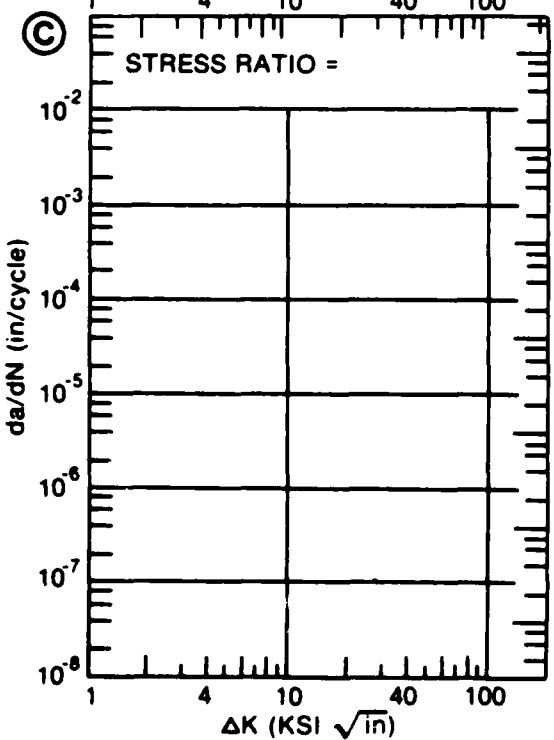
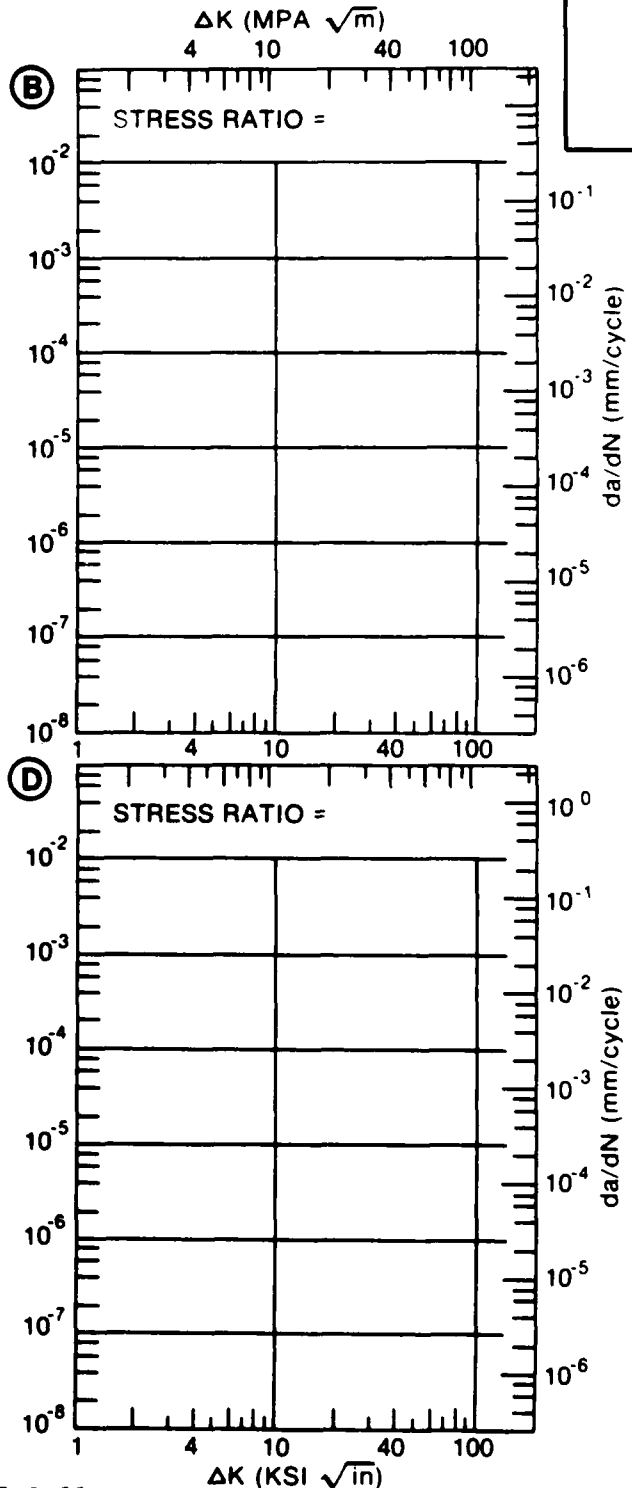
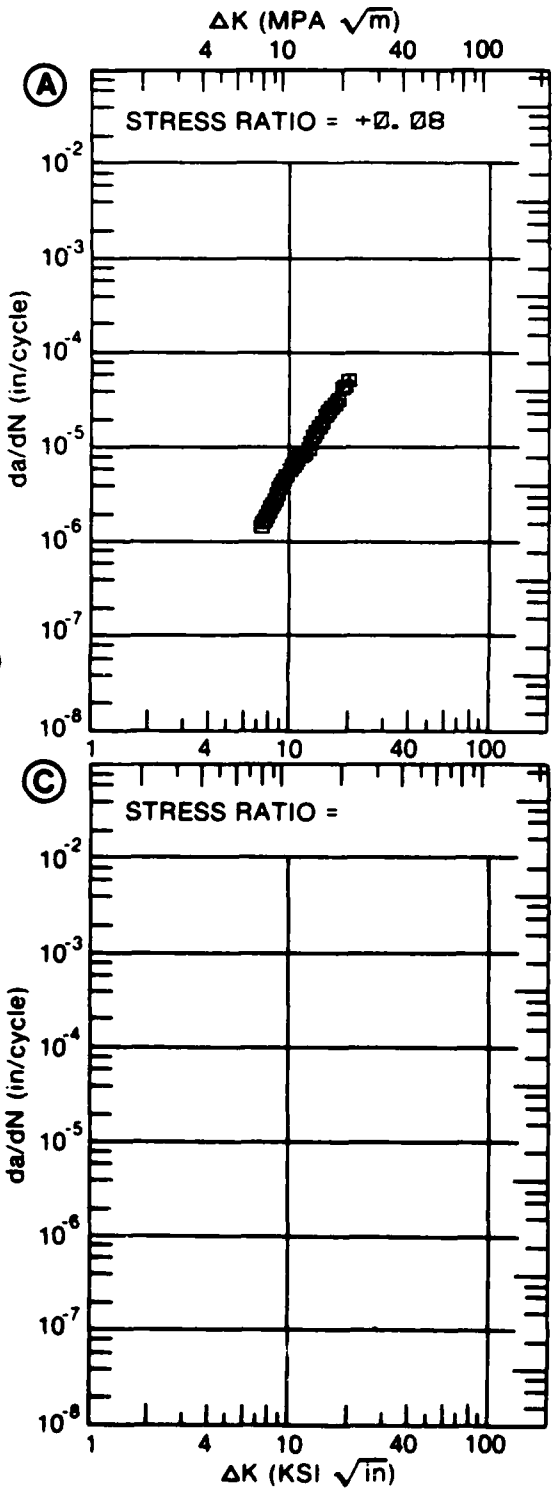


Figure 7.5.3.66

TABLE 7.5.3.67

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.67 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.30			
DELTA K MIN	A: 6.19	2.25			
	B:				
	C:				
	D:				
	7.00	3.42			
	8.00	5.46			
	9.00	8.45			
	10.00	12.9			
DELTA K MAX	A: 12.46	36.2			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		11.31			
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	0.5-0.8	0.8-1.25	1.25-2.0	>2.0
				1	

CONDITION/HT: T851
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 86.0 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 6.000"
 REFERENCES 98579

ALUM. ALLOY
2024

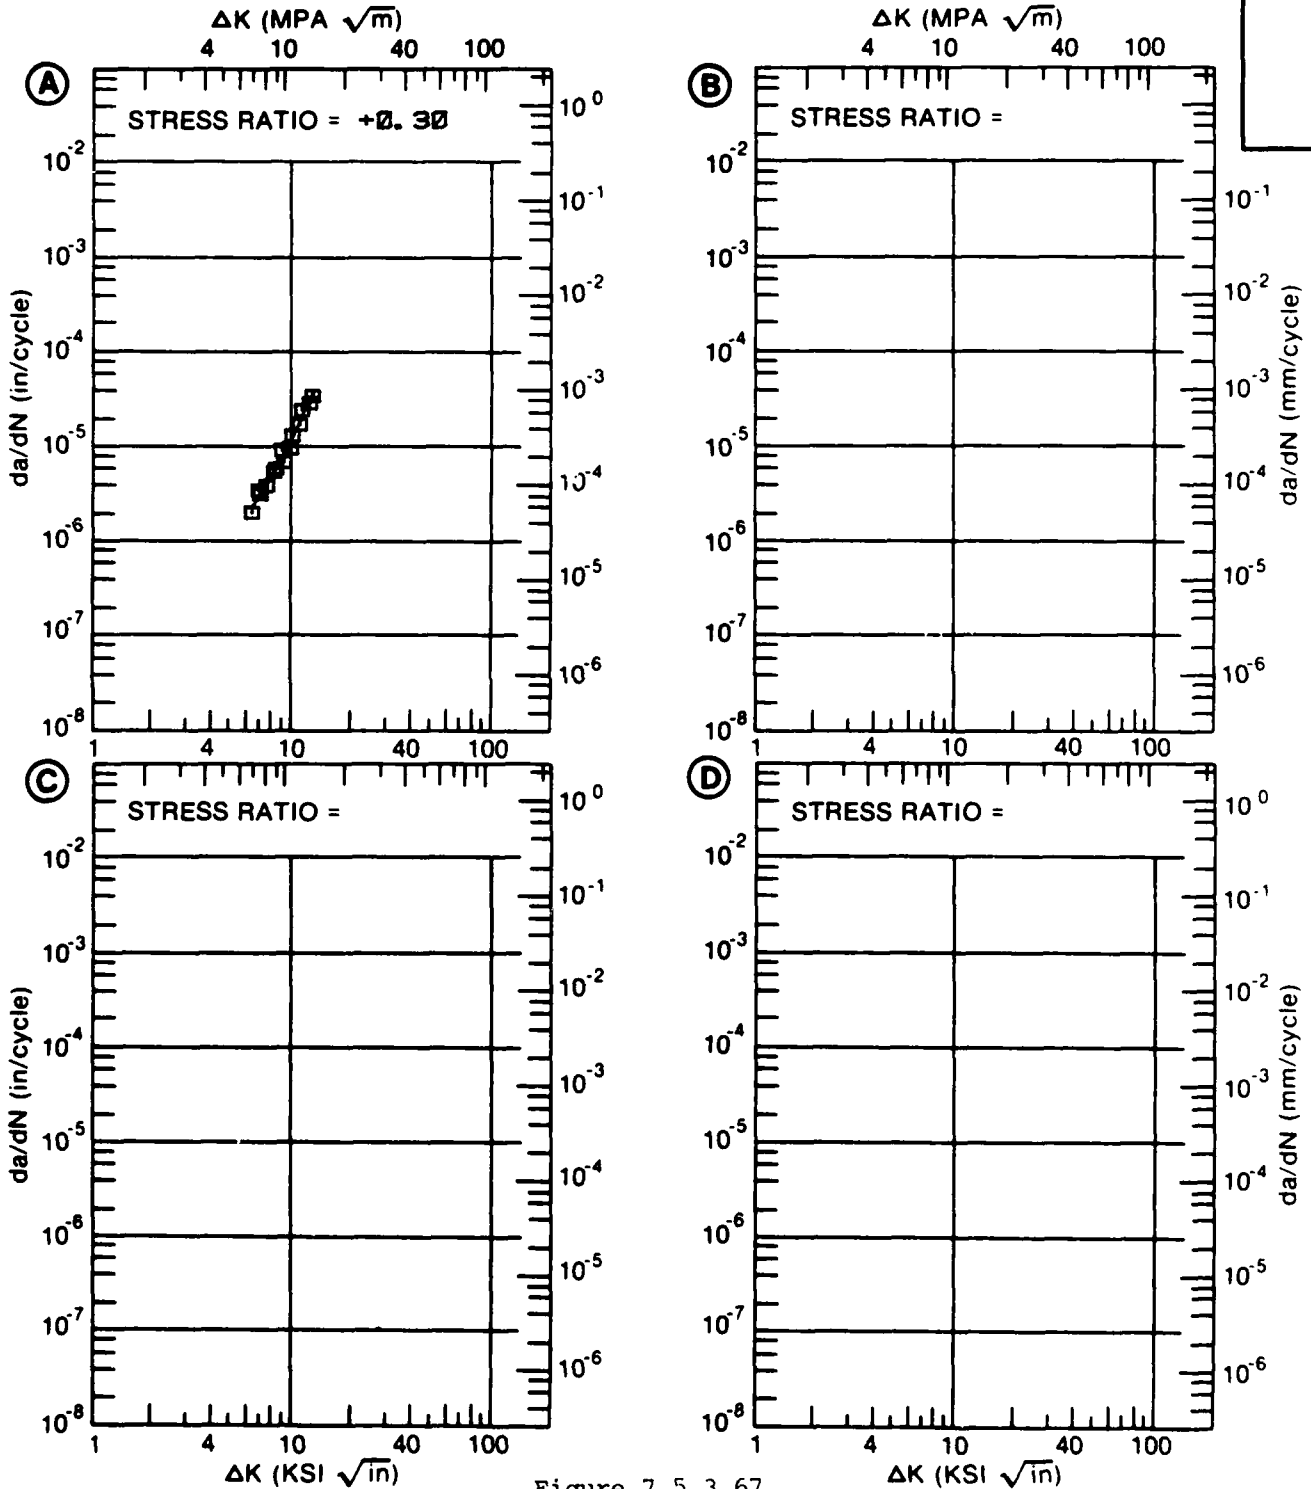


Figure 7.5.3.67

TABLE 7.5.3.68

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.68 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 2024
CONDITION: T851

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. J. P. 4	E= R. T. DIST. H20	E= R. T. S. T. W.
DELTA K	A: 7.16	1.75			
MIN	B: 5.85		.987		
	C: 5.87			1.51	
	D: 7.37				2.71
	6.00		1.13	1.57	
	7.00		2.38	2.43	
	8.00	2.99	4.06	3.79	3.52
	9.00	4.91	6.12	5.22	5.34
	10.00	7.27	8.55	6.99	7.92
	13.00	17.4	19.	23.0	19.8
	16.00	34.8	39.5	112.	35.6
	20.00		108.		112.
DELTA K	A: 19.69	78.9			
MAX	B: 21.48		241.		
	C: 16.35			211.	
	D: 22.77				415.
ROOT MEAN SQUARE		15.20	10.17	21.77	15.52
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	1	1	2

CONDITION/HT: T851
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 59.0- 66.0 KSI
 ULT. STRENGTH: 71.0- 74.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 5.990- 6.000"
 REFERENCES: 88579

ALUM.
 ALLOY
 2024

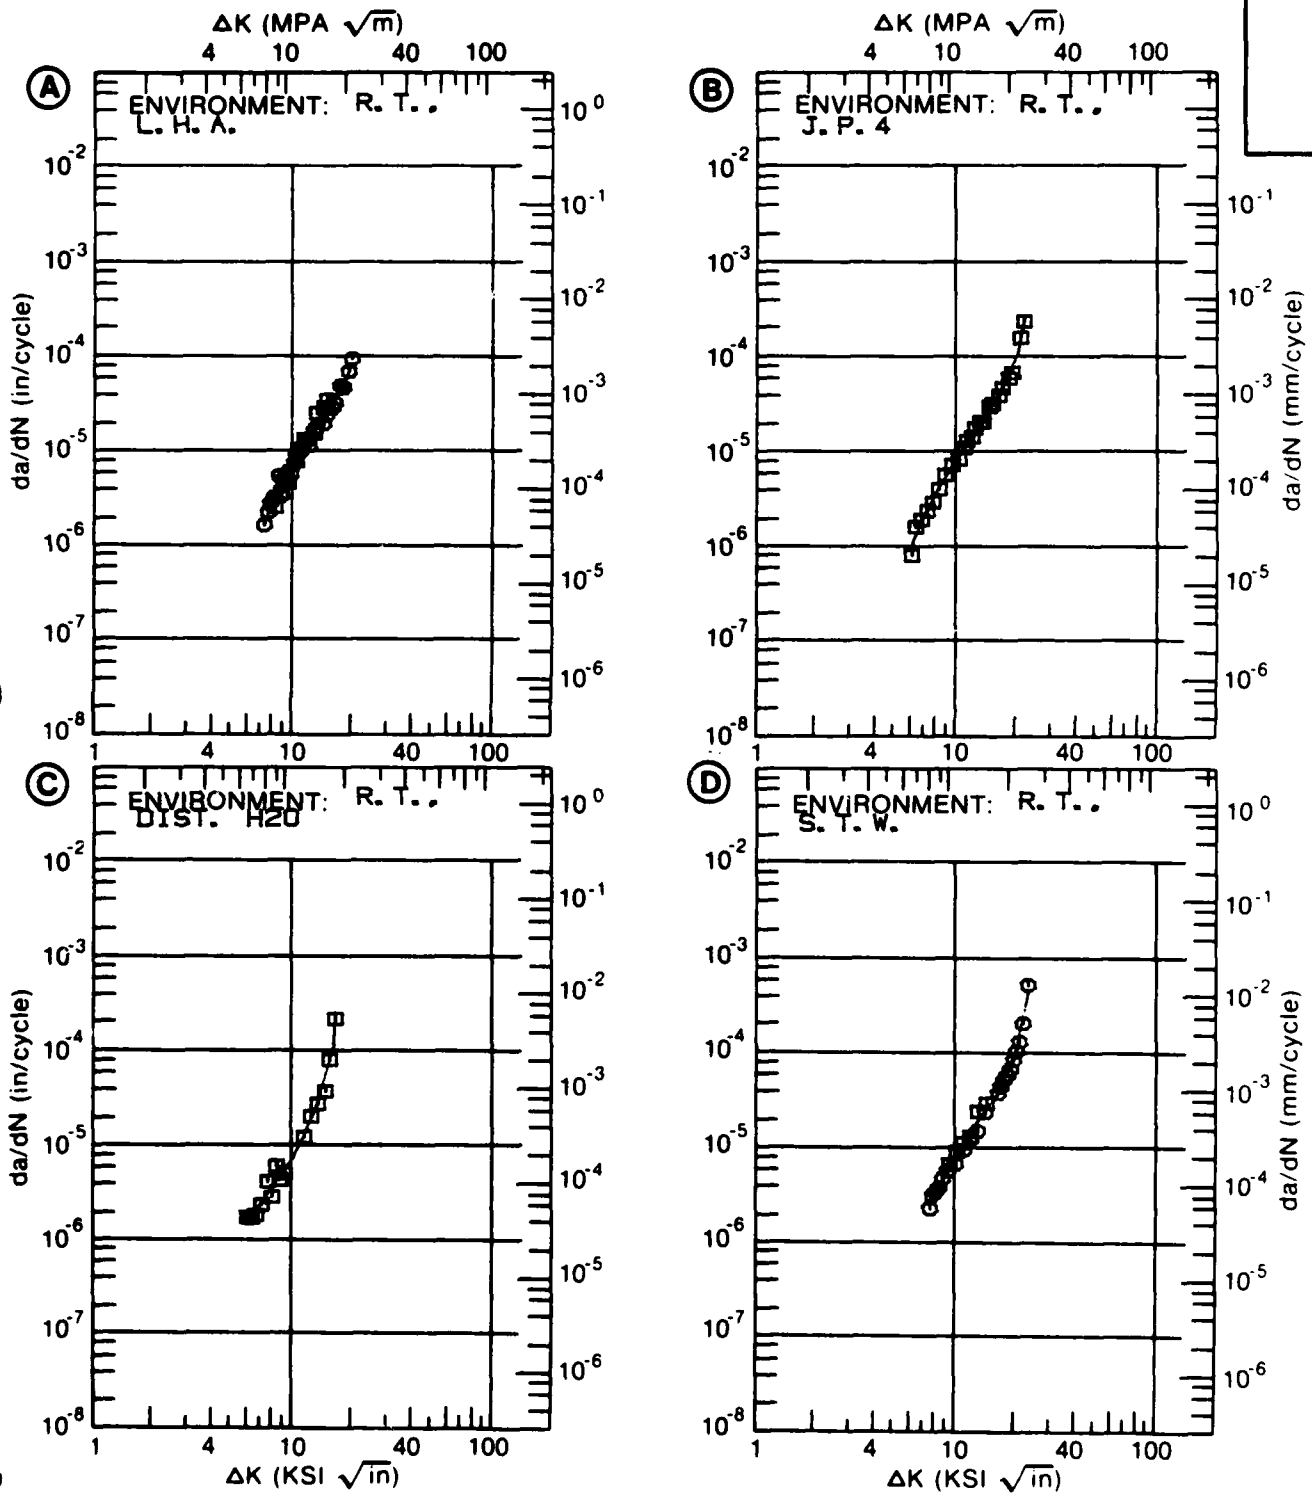


Figure 7.5.3.68

TABLE 7.5.3.69

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.69 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM 2024
CONDITION: T851
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	F(HZ)= 1.00		F(HZ)= 6.00	
DELTA K MIN	A: 9.67 : B: 6.86 : C: : D: :	4.65	1.67	
	7.00 : 8.00 : 9.00 : 10.00 : 13.00 : 16.00 :	5.90 17.6 50.2	1.92 4.12 6.66 9.45 24.5	
DELTA K MAX	A: 16.70 : B: 15.93 : C: : D: :	72.4	88.2	

ROOT MEAN SQUARE 13.07 13.08
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 65.0 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.990- 6.000"
 REFERENCES: 88579

ALUM.
ALLOY

2024

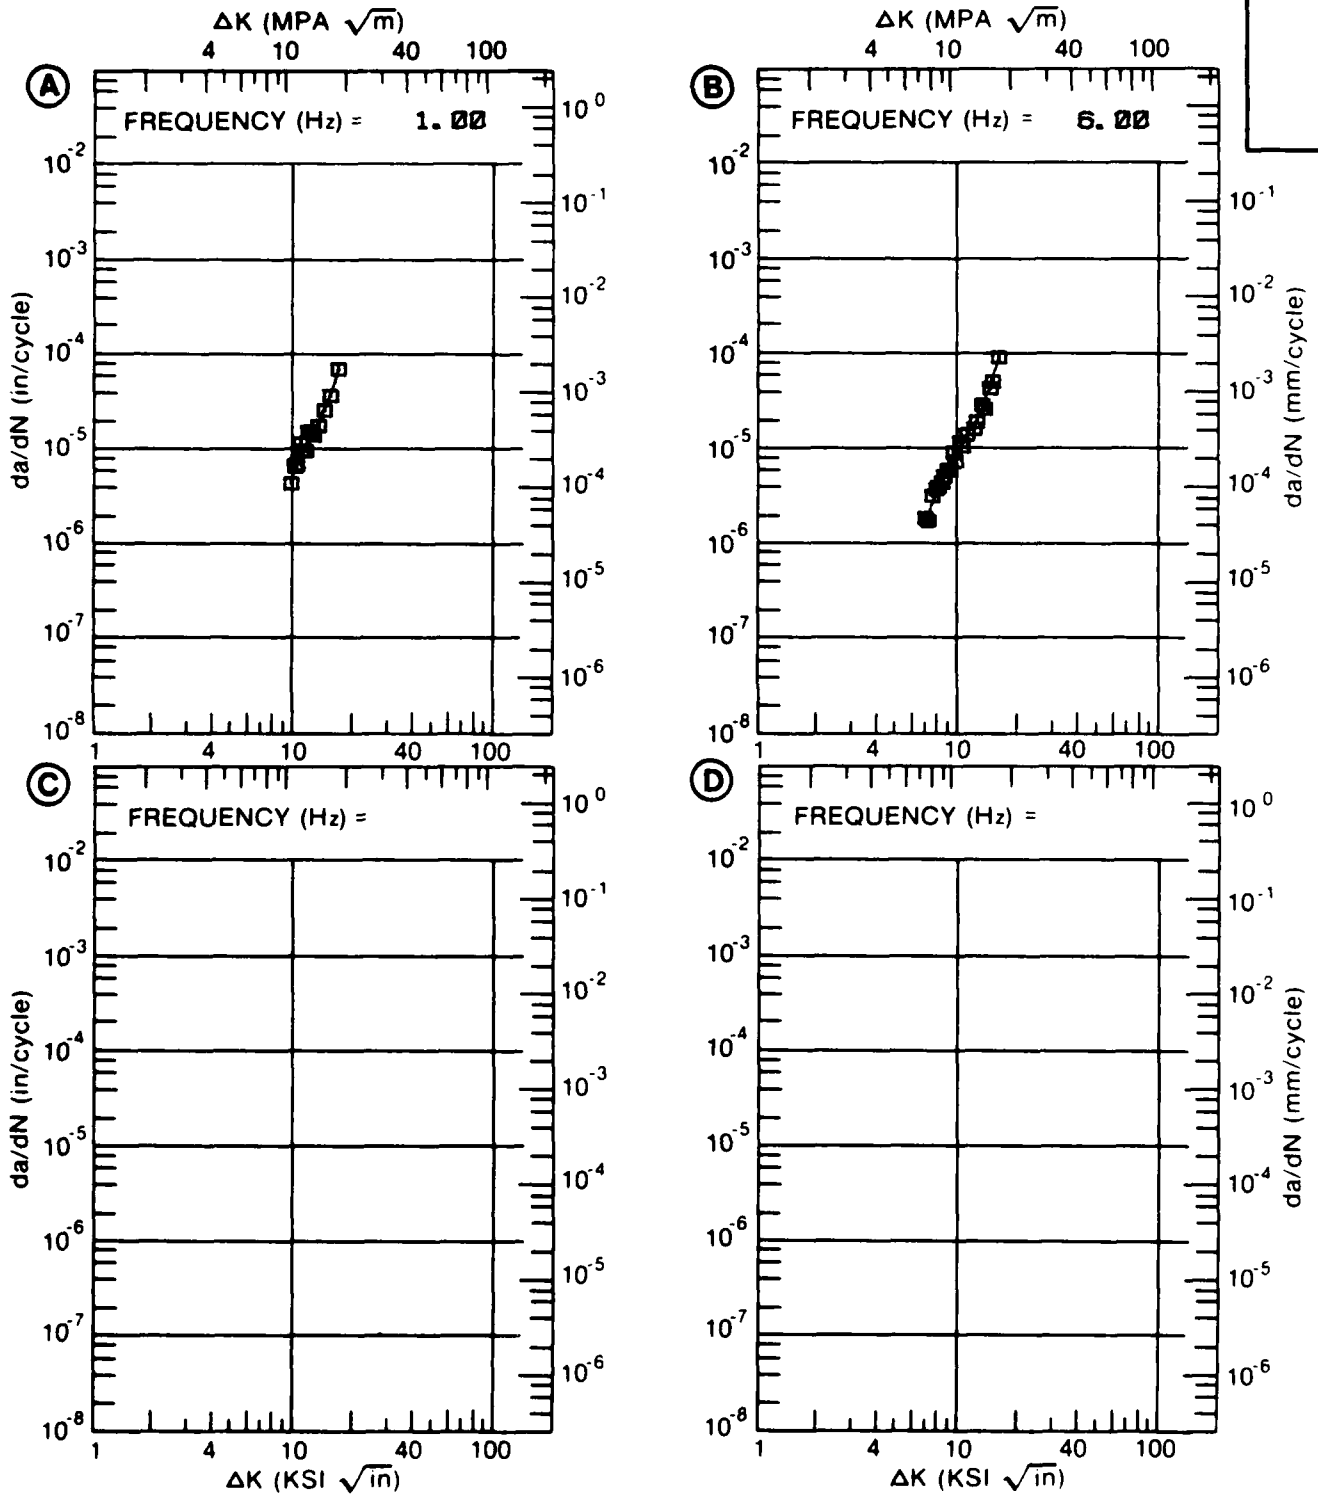


Figure 7.5.3.69

TABLE 7.5.3.70

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.70 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T851					
ENVIRONMENT: R. T. , 3.5% NaCl					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 8.35	9.90			
	B:				
	C:				
	D:				
	9.00	10.5			
	10.00	18.2			
	13.00	62.2			
DELTA K MAX	A: 14.30	228.			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		38.36			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	2			
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 0.10- 10.00 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 64.6 KSI
 ULT. STRENGTH: 71.3 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: 90981

ALUM.
ALLOY

2024

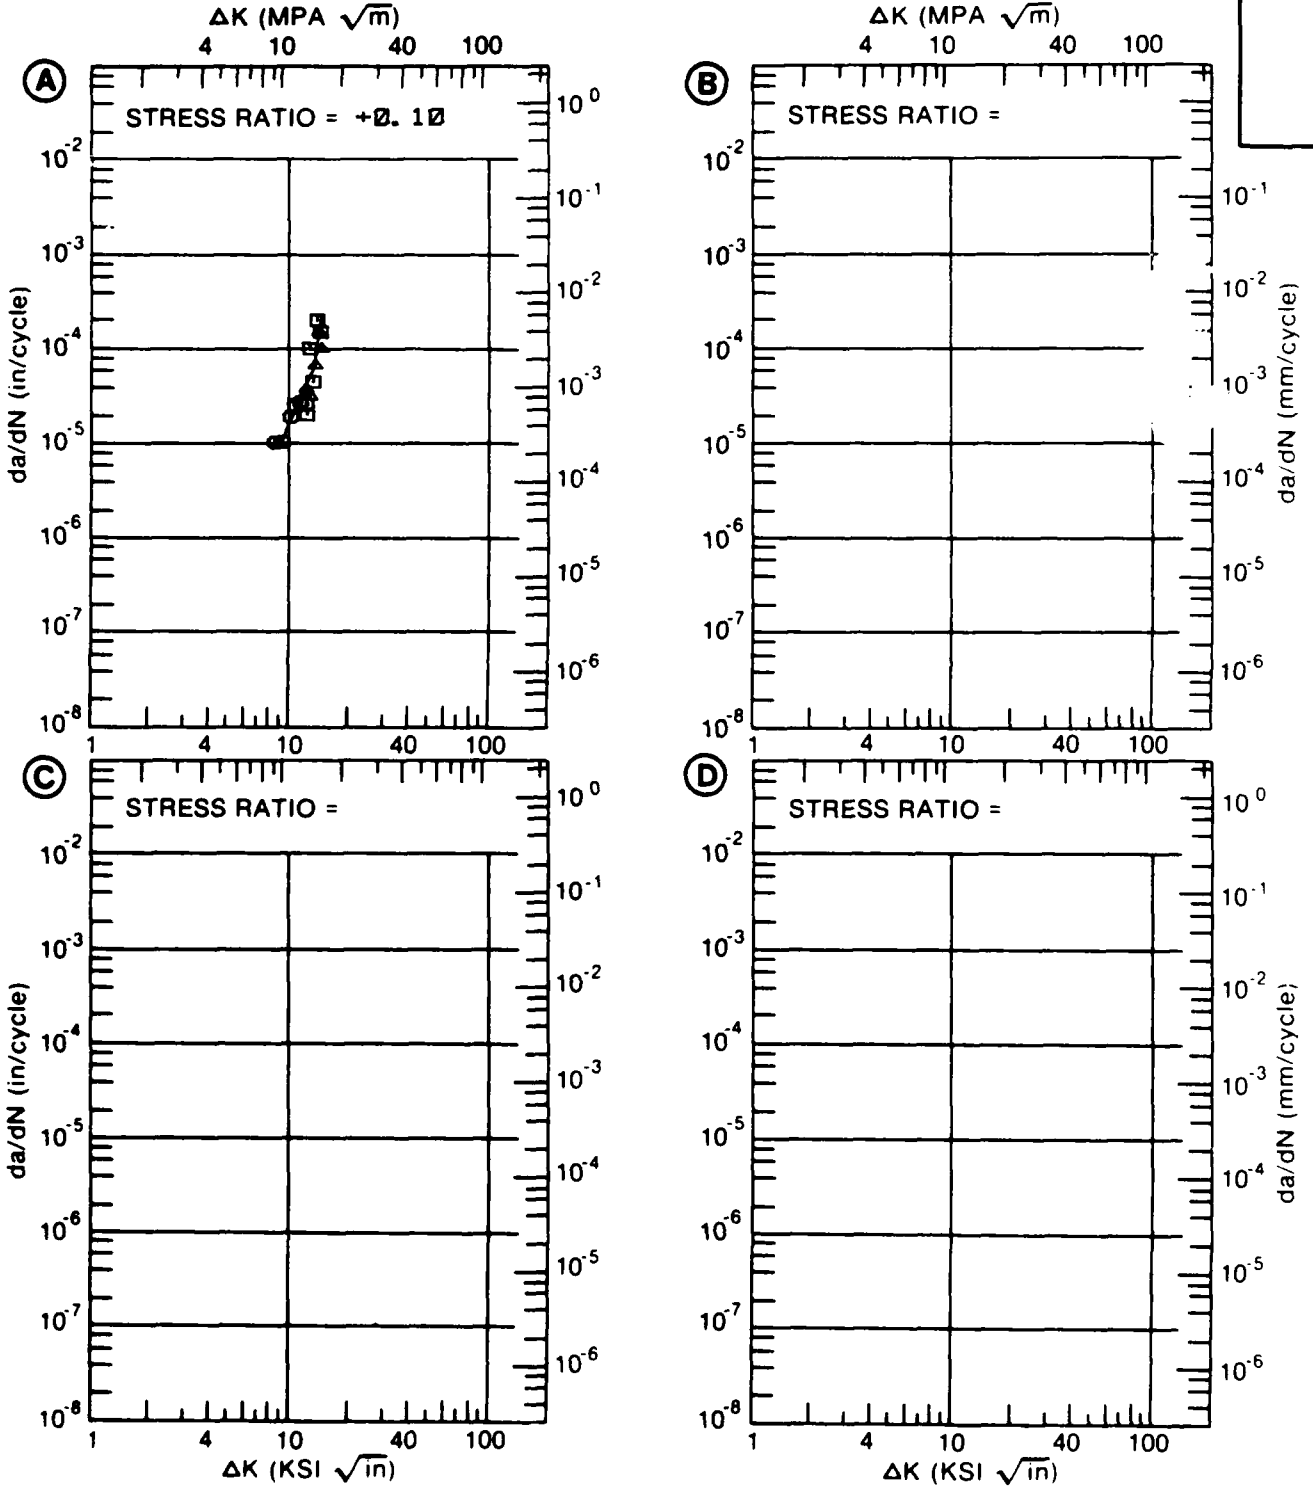


Figure 7.5.3.70

TABLE 7.5.3.71

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.71 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T852					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 5.43	1.19			
	B:				
	C:				
	D:				
	6.00	1.36			
	7.00	1.74			
	8.00	2.25			
	9.00	2.91			
	10.00	3.72			
	13.00	7.43			
	16.00	13.6			
	20.00	27.4			
DELTA K MAX	A: 21.81	36.3			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		19.83			
PERCENT ERROR					
LIFE PREDICTION	0.0-0.5				
RATIO SUMMARY	0.5-0.8				
(NP/NA)	0.8-1.25	3			
	1.25-2.0				
	>2.0				

CONDITION/HT: T852
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 53.0 KSI
 ULT. STRENGTH: 68.0- 70.0 KSI
 SPECIMEN THK: 0.250- 0.502"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579, 85837

ALUM.
ALLOY

2024

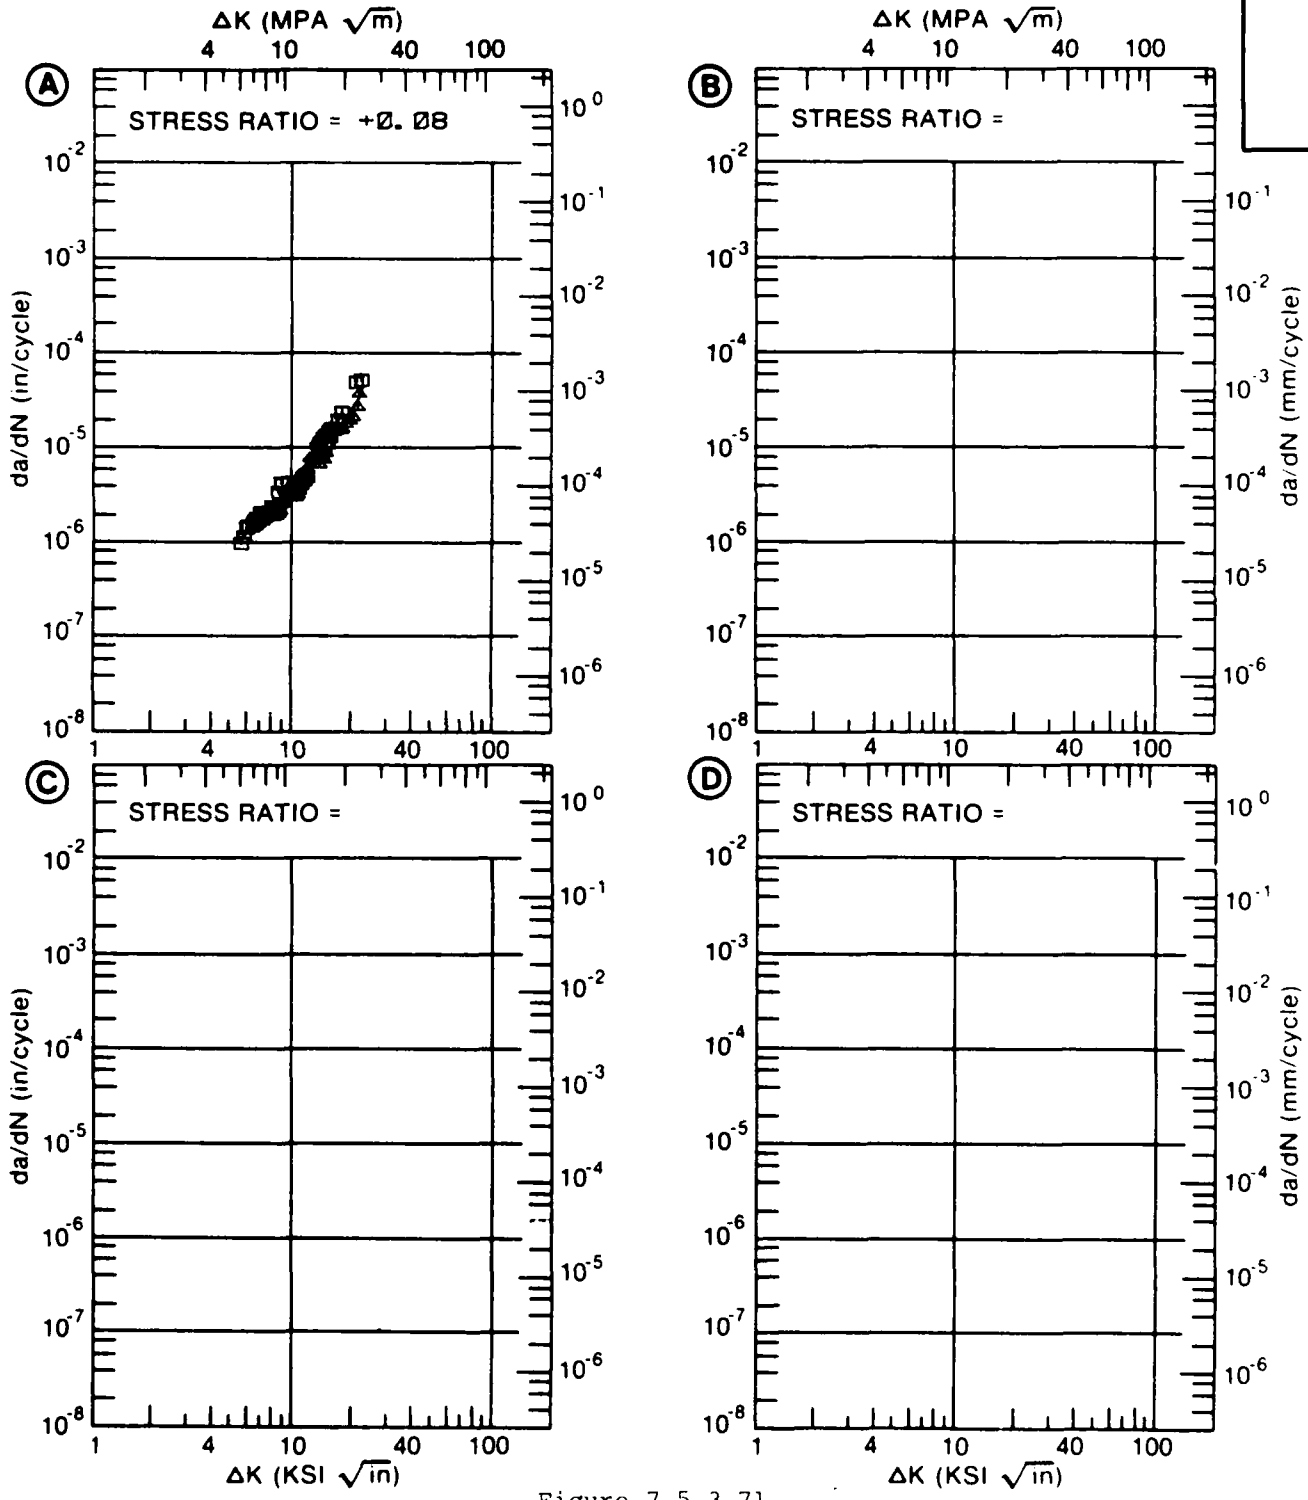


Figure 7.5.3.71

TABLE 7.5.3.72

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.72 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		S. C. S.			
DELTA K MIN	A: 4.09	: .688			
	B:	:			
	C:	:			
	D:	:			
	5.00	: 1.69			
	6.00	: 2.36			
	7.00	: 3.49			
	8.00	: 5.12			
	9.00	: 7.30			
	10.00	: 9.98			
	13.00	: 19.8			
DELTA K MAX	A: 14.86	: 25.5			
	B:	:			
	C:	:			
	D:	:			
ROOT MEAN SQUARE		9.72			
PERCENT ERROR					
LIFE PREDICTION	0.0-0.5				
RATIO	0.5-0.8				
SUMMARY (NP/NA)	0.8-1.25	: 1			
	1.25-2.0				
	>2.0				

CONDITION/HT: T852
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 53.0 KSI
 ULT. STRENGTH: 70.0 KSI
 SPECIMEN THK: 1.004"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

ALUM. ALLOY
2024

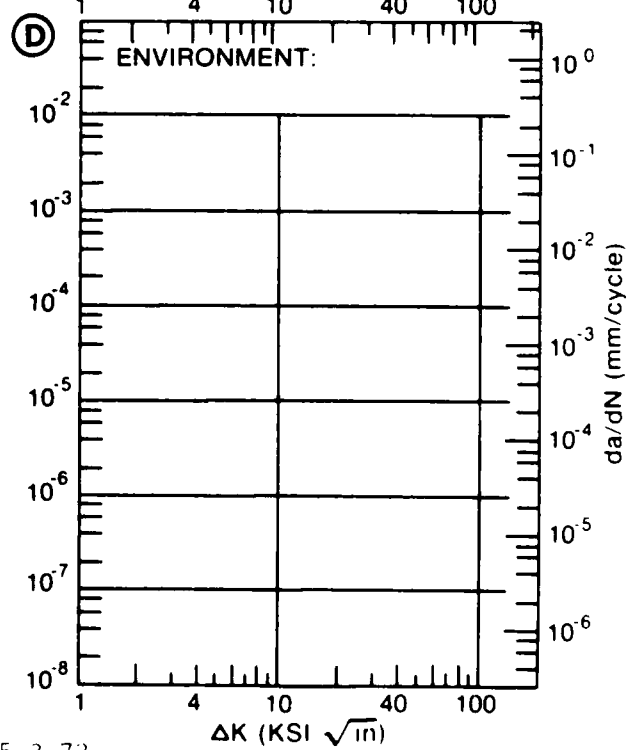
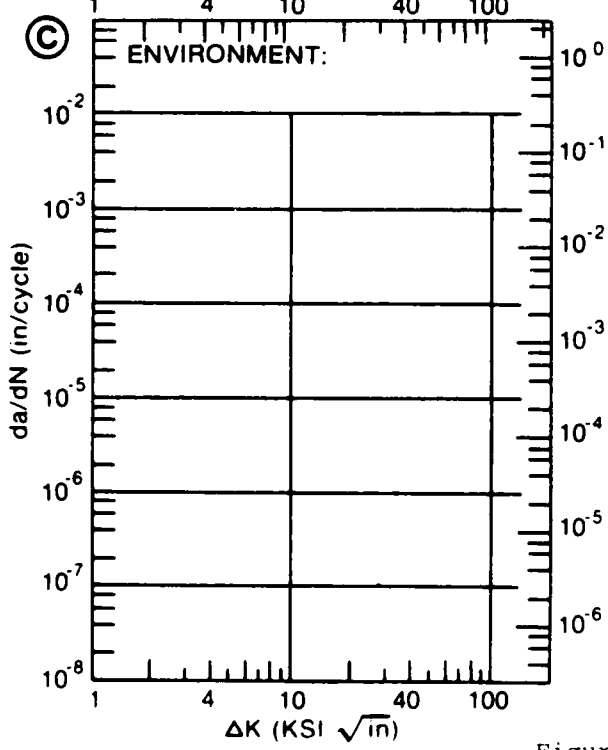
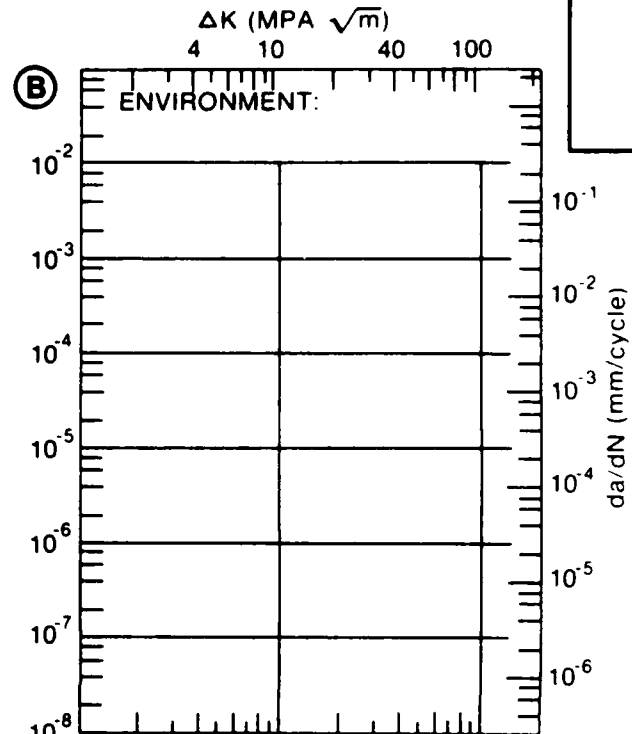
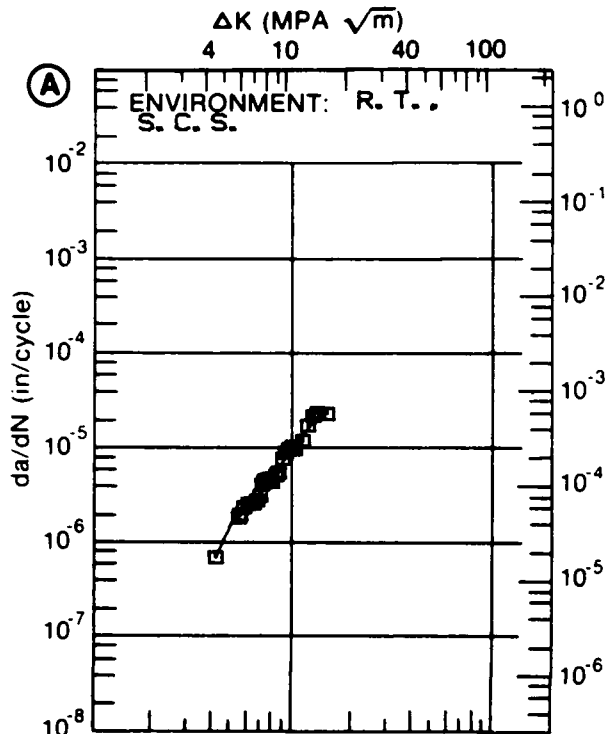


Figure 7.5.3.72

TABLE 7.5.3.73

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.73 INDICATING EFFECT

OF FREQUENCY

MATERIAL: ALUMINUM 2024
CONDITION: T852
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10**--6 IN. /CYCLE)			
	A	B	C	D
	F(HZ)= 0.10		F(HZ)= 1.00	
DELTA K MIN	A: 6.91	1.57	B: 3.80	.373
	C:		D:	
	4.00			.462
	5.00			1.06
	6.00			1.94
	7.00	1.65		3.14
	8.00	2.73		4.75
	9.00	4.12		6.90
	10.00	5.88		9.81
	13.00	14.7		26.3
	16.00	34.4		
DELTA K MAX	A: 16.31	37.6	B: 14.60	43.9
	C:		D:	

ROOT MEAN SQUARE 6.74 17.41
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T852
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 53.0 KSI
 ULT. STRENGTH: 70.0 KSI
 SPECIMEN THK: 1.000- 1.002"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

ALUM.
ALLOY

2024

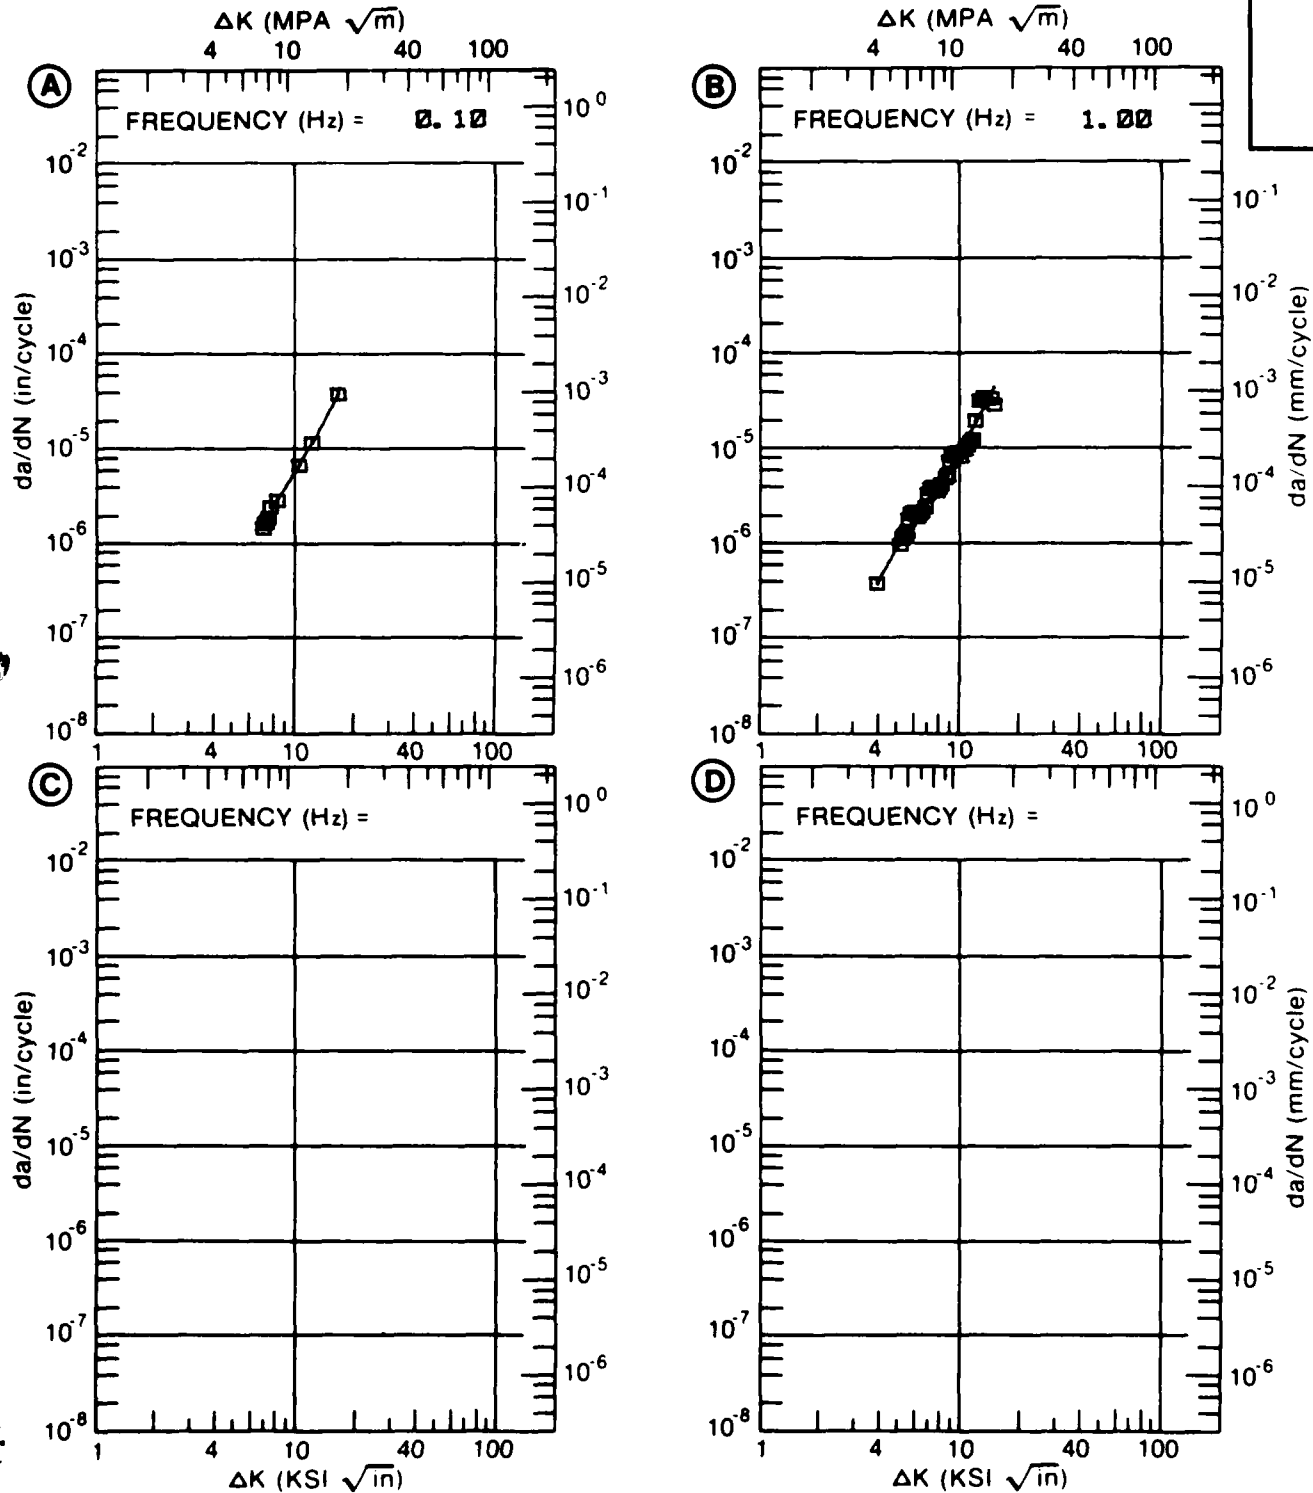


Figure 7.5.3.73

TABLE 7.5.3.74

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.74 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E=+ 265F			
		L. H. A			
DELTA K	A: 6.27	1.60			
MIN	B:				
	C:				
	D:				
	7.00	2.50			
	8.00	4.25			
	9.00	6.77			
	10.00	10.3			
	13.00	29.2			
	16.00	74.9			
DELTA K	A: 17.44	155.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		15.22			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T852
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 54.0 KSI
 ULT. STRENGTH: 68.0 KSI
 SPECIMEN THK: 0.999"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

ALUM. ALLOY
2024

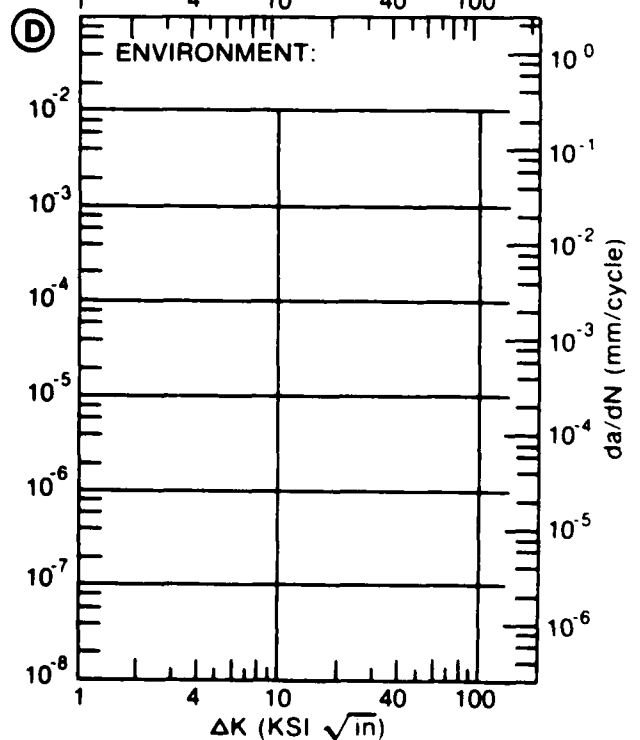
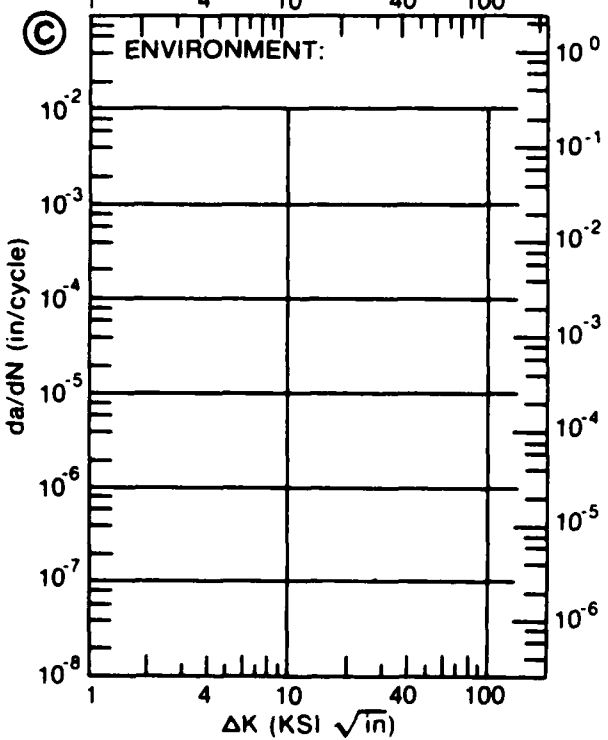
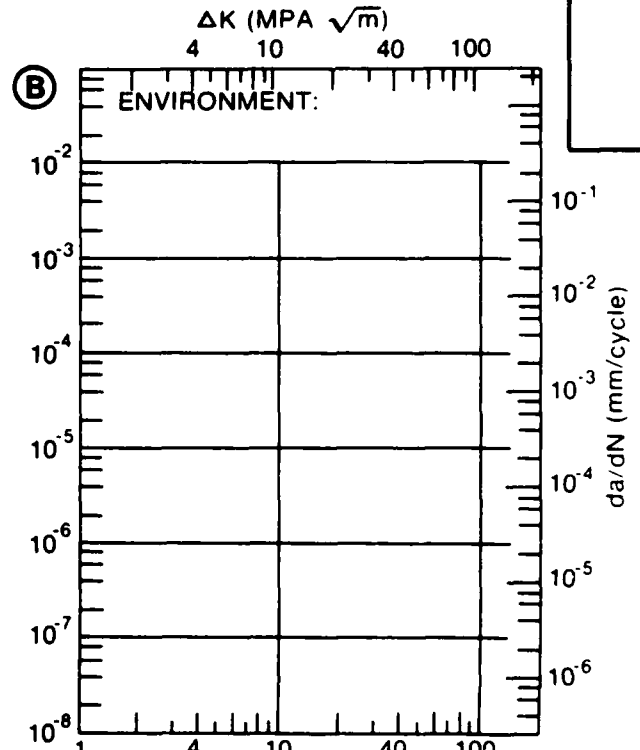
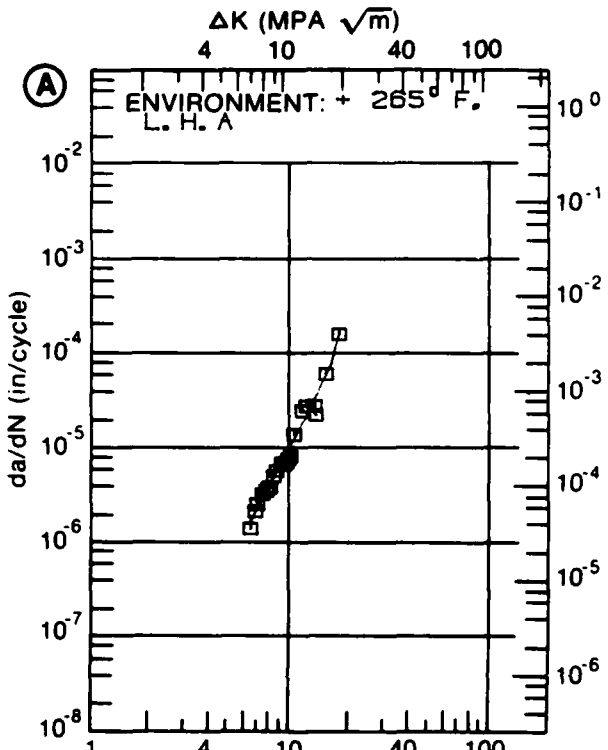


Figure 7.5.3.74

TABLE 7.5.3.75

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.75 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2024			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		S. T. W.			
DELTA K A:	8.03	2.81			
DELTA K B:					
MIN C:					
D:					
	9.00	3.50			
	10.00	5.19			
	13.00	18.5			
DELTA K A:	15.99	36.5			
DELTA K B:					
MAX C:					
D:					
ROOT MEAN SQUARE		22.22			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T852
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 54.0 KSI
 ULT. STRENGTH: 68.0 KSI
 SPECIMEN THK: 0.998- 0.999"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

ALUM. ALLOY
2024

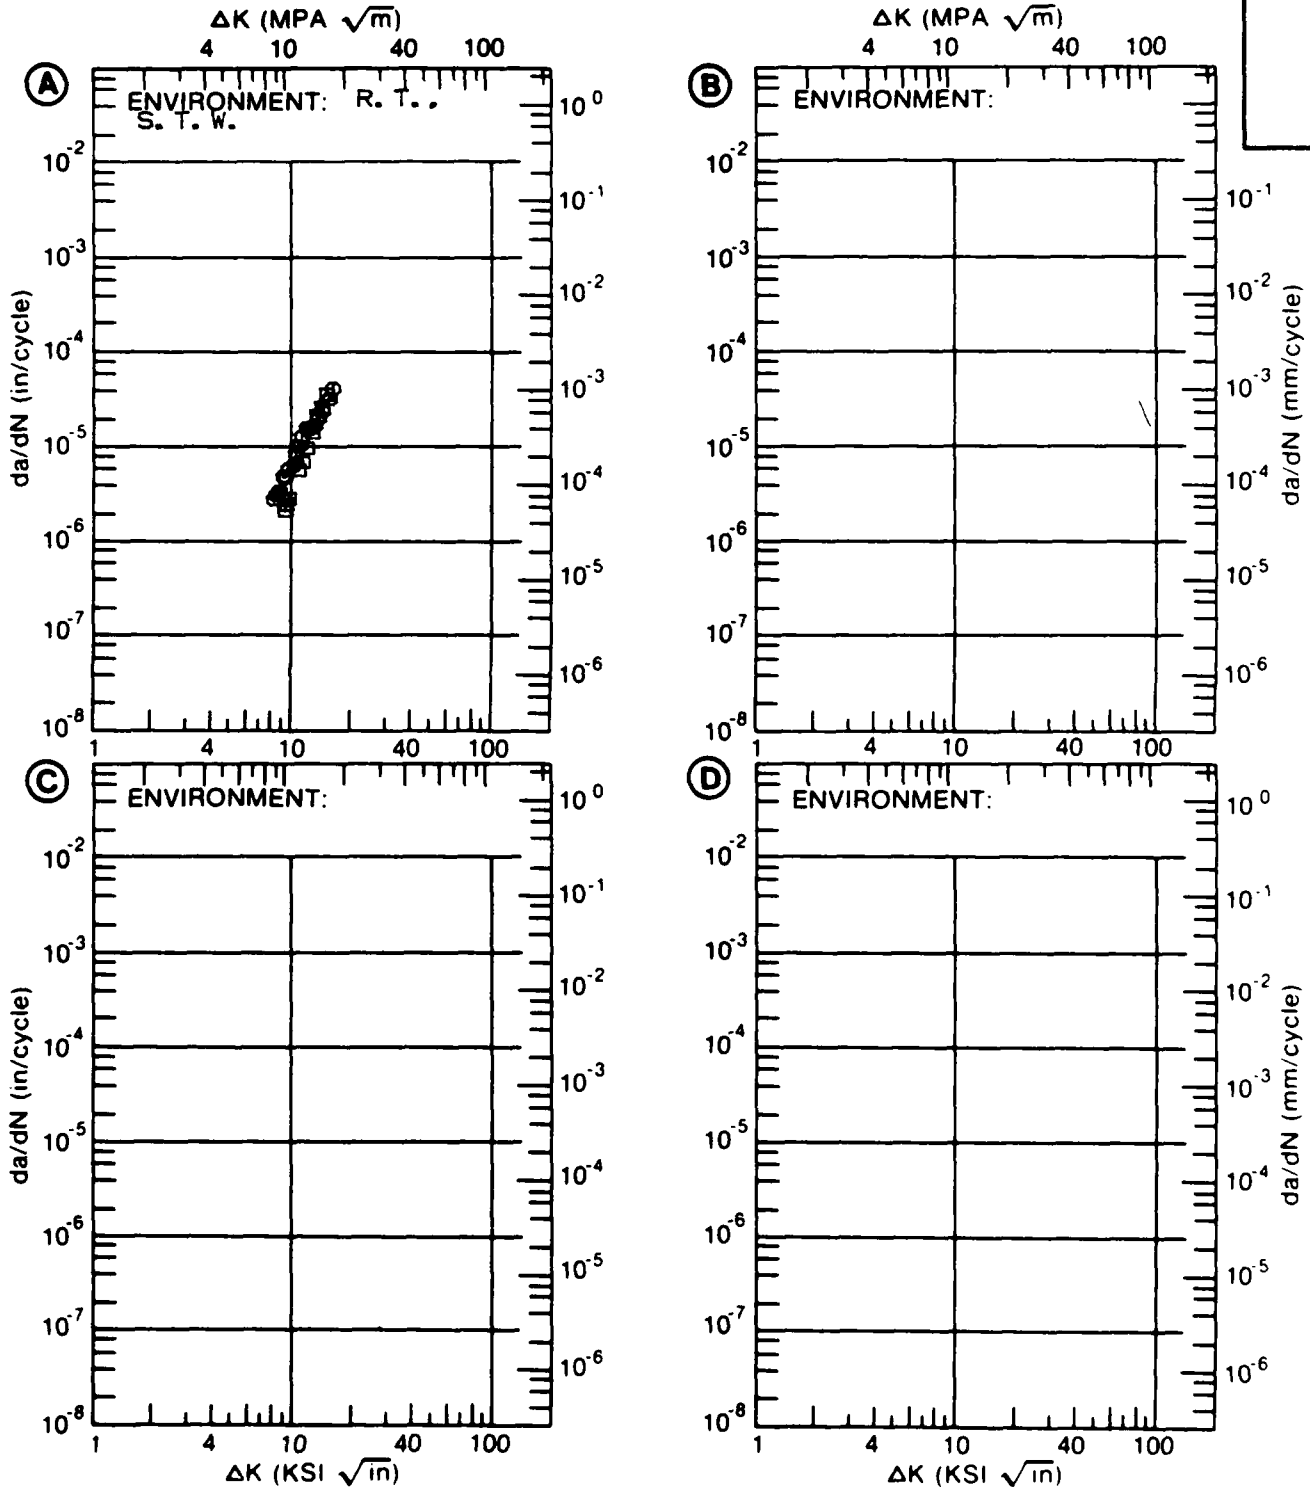


Figure 7.5.3.75

TABLE 7.5.3.76

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.76 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T852					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.33			
DELTA K	A: 6.07	1.26			
MIN	B:				
	C:				
	D:				
	7.00	2.13			
	8.00	3.14			
	9.00	4.25			
	10.00	5.59			
	13.00	13.5			
DELTA K	A: 15.89	39.3			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		30.64			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8	1			
RATIO	0.8-1.25	4			
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: T852
 FORM: 6.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 5.17 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 77720

ALUM. ALLOY
2024

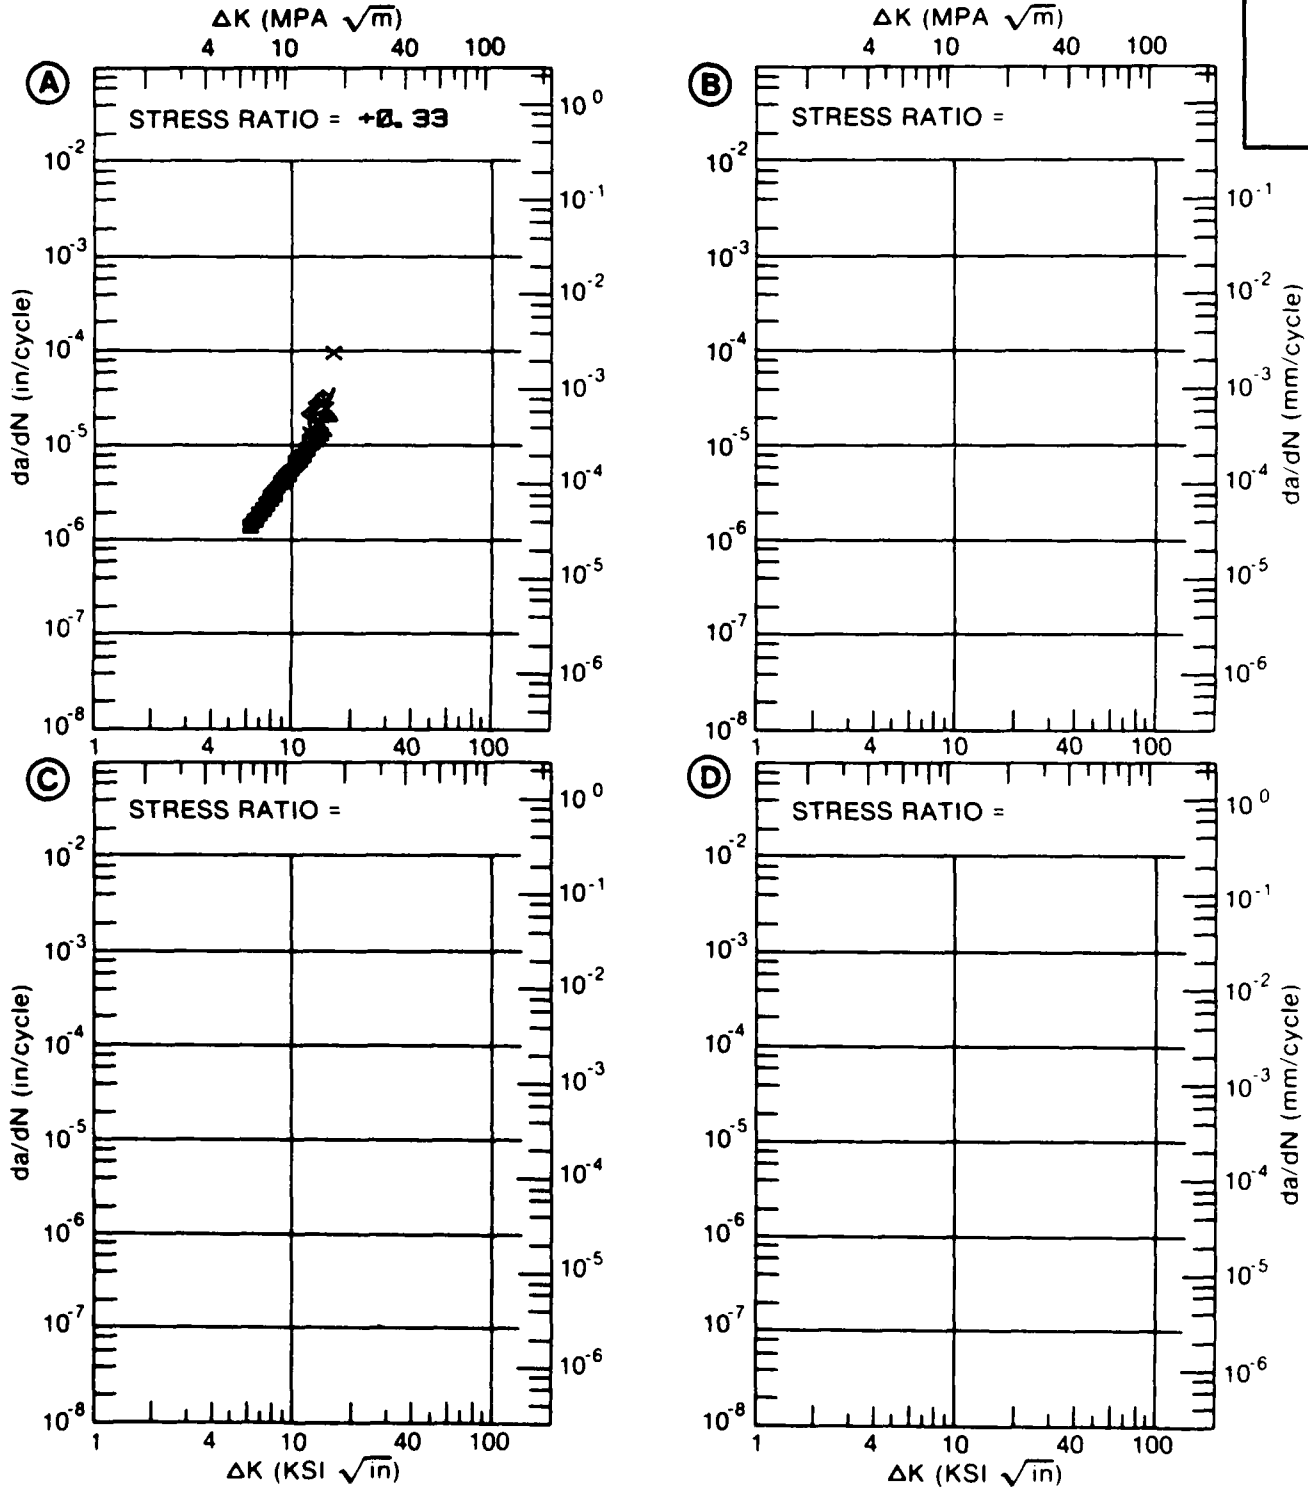


Figure 7.5.3.76

TABLE 7.5.3.77

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.77 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: TB61
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 20.67	104.			
	B:				
	C:				
	D:				
	25.00	236.			
	30.00	570.			
	35.00	3094.			
DELTA K MAX	A: 38.64	20484.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 31.76
PERCENT ERROR

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	1
	0.5-0.8	4
	0.8-1.25	3
	1.25-2.0	1
	>2.0	

CONDITION/HT: T861
 FORM: 0.02" TH SHEET
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 0.10- 1.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 65.7 KSI
 ULT. STRENGTH: 70.8 KSI
 SPECIMEN THK: 0.020"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

ALUM. ALLOY
2024

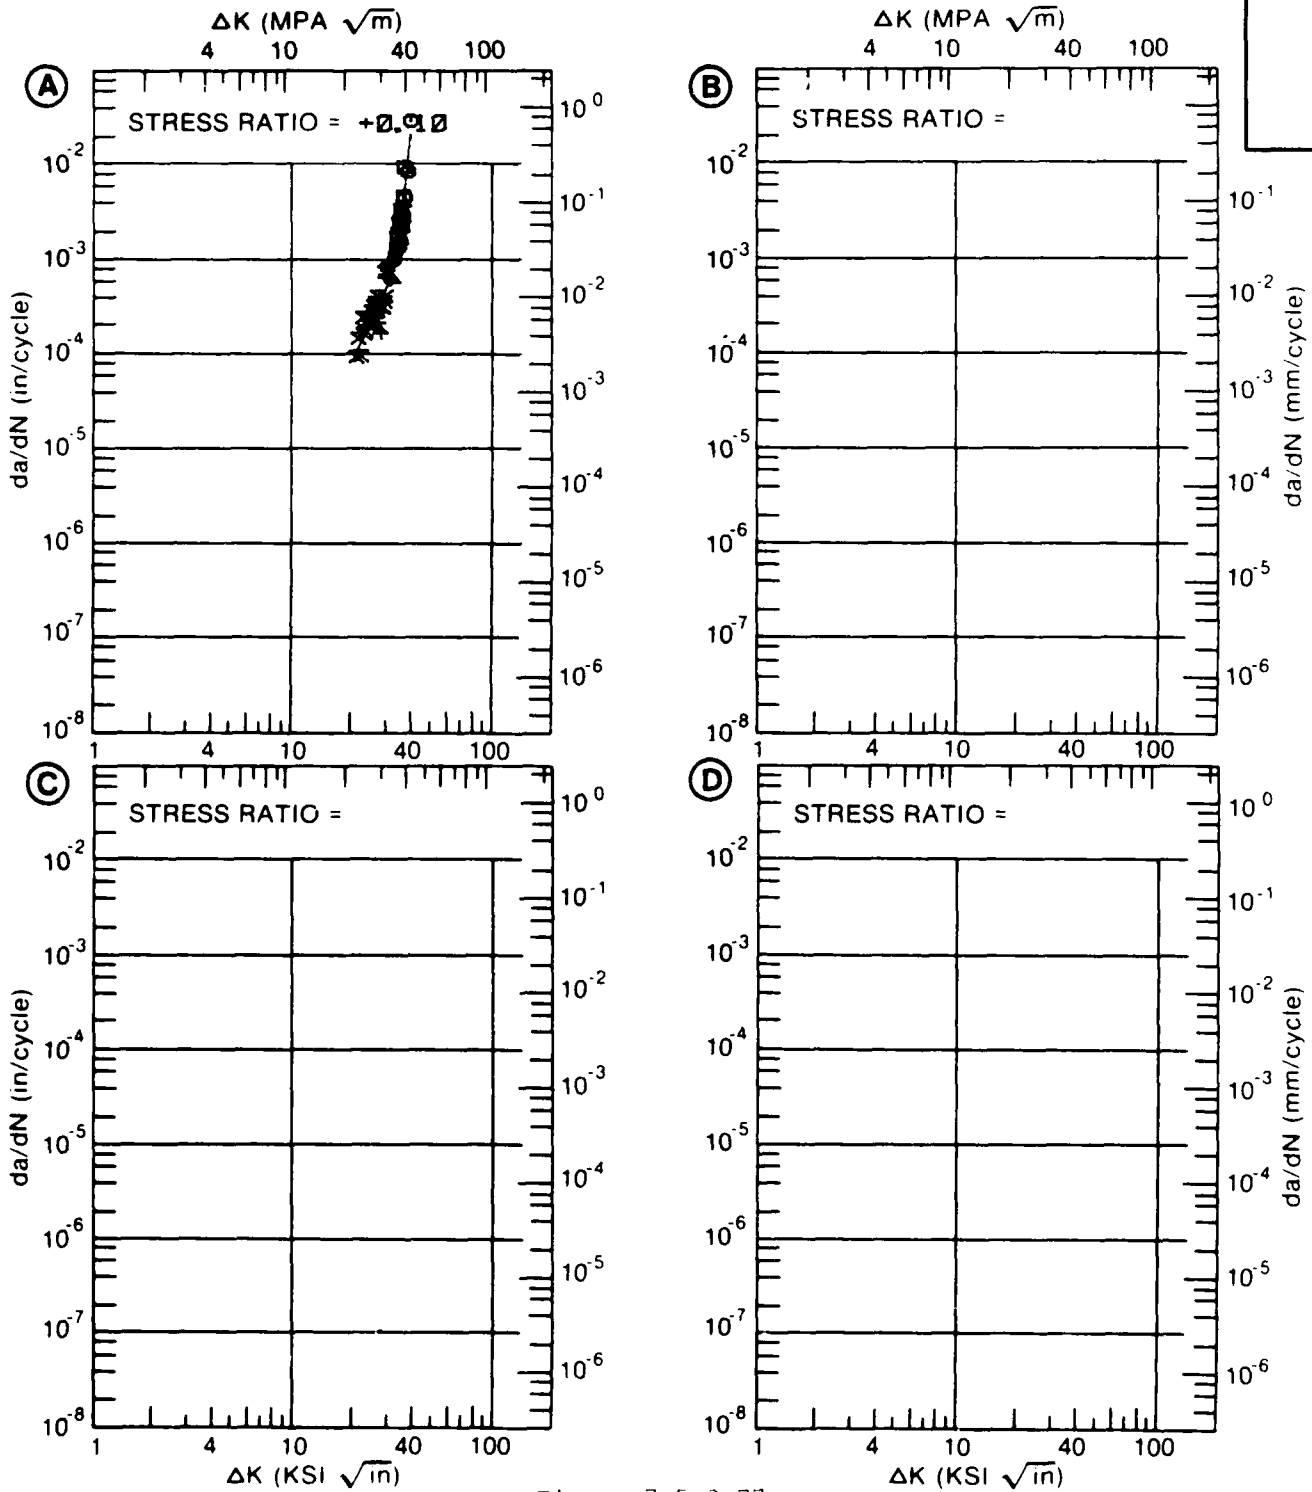


Figure 7.5.3.77

TABLE 7.5.3.78

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.78 INDICATING EFFECT

OF FREQUENCY

MATERIAL: ALUMINUM		2024	
CONDITION: T861			
ENVIRONMENT: R. T. , LAB AIR			
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)	
		A	B
		F(HZ)= 2.00-9.00	F(HZ)= 10.00-13.00
			C
			D
DELTA K	A: 8.65	4.75	
MIN	B: 3.38		.438
	C:		
	D:		
	3.50		.463
	4.00		.591
	5.00		.998
	6.00		1.68
	7.00		2.73
	8.00		4.27
	9.00	6.59	6.44
	10.00	8.06	9.37
	13.00	17.4	24.1
	16.00	40.3	49.8
	20.00	99.9	
DELTA K	A: 22.81	156.	
MAX	B: 18.90		86.5
	C:		
	D:		
ROOT MEAN SQUARE		14.48	22.93
PERCENT ERROR			
LIFE	0.0-0.5		
PREDICTION	0.5-0.8		
RATIO	0.8-1.25	4	9
SUMMARY	1.25-2.0		
(NP/NA)	>2.0		

CONDITION/HT: T861
 FORM: 0.02" TH SHEET
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 65.7 KSI
 ULT. STRENGTH: 70.8 KSI
 SPECIMEN THK: 0.020"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

ALUM. ALLOY
2024

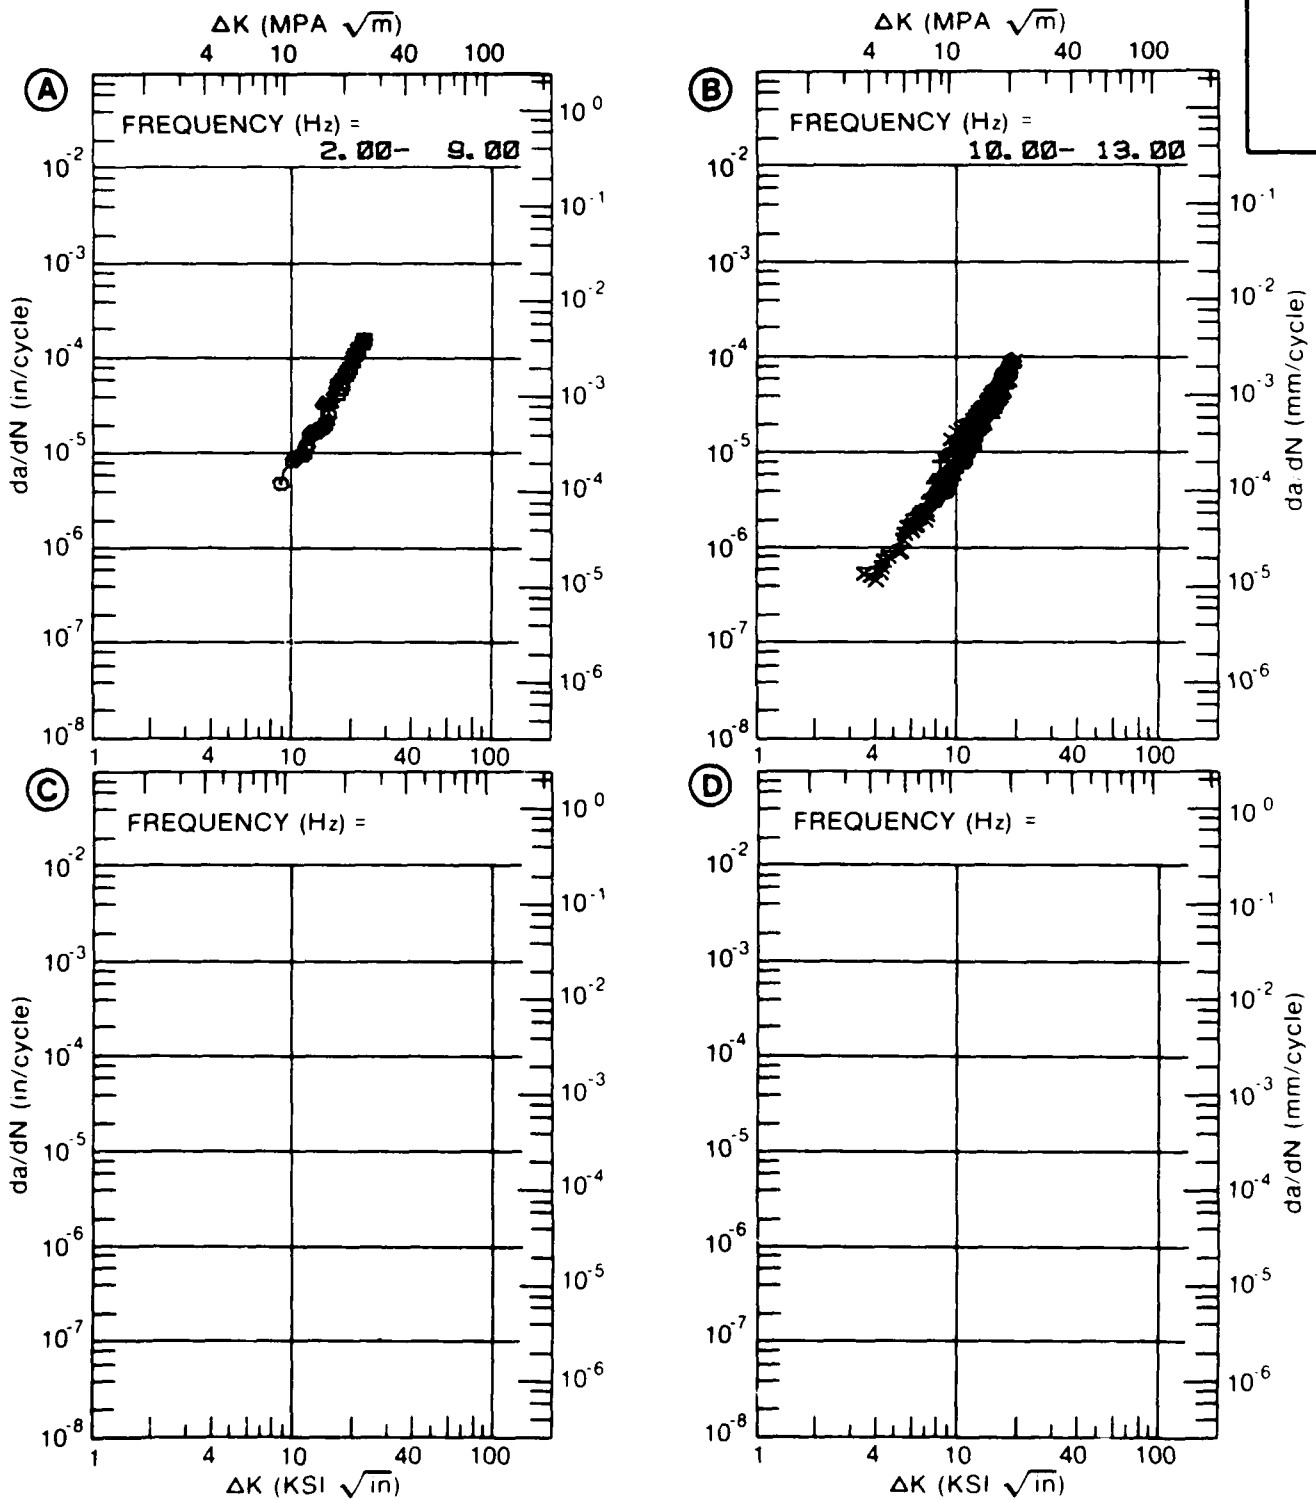


Figure 7.5.3.78

TABLE 7.5.3.79

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.79 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T861					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.10		
DELTA K A:	4.55	.48			
DELTA K B:					
MIN C:					
D:					
	5.00	.710			
	6.00	1.40			
	7.00	2.41			
	8.00	3.87			
	9.00	5.99			
	10.00	9.12			
	13.00	31.4			
	16.00	111.			
	20.00	595.			
	25.00	2845.			
DELTA K A:	26.94	11616.			
DELTA K B:					
MAX C:					
D:					
ROOT MEAN SQUARE		19.73	0.00		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	3			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T861
 FORM: 0.09" TH SHEET
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 0.10- 15.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 73.0 KSI
 ULT. STRENGTH: 76.6 KSI
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

ALUM.
ALLOY

2024

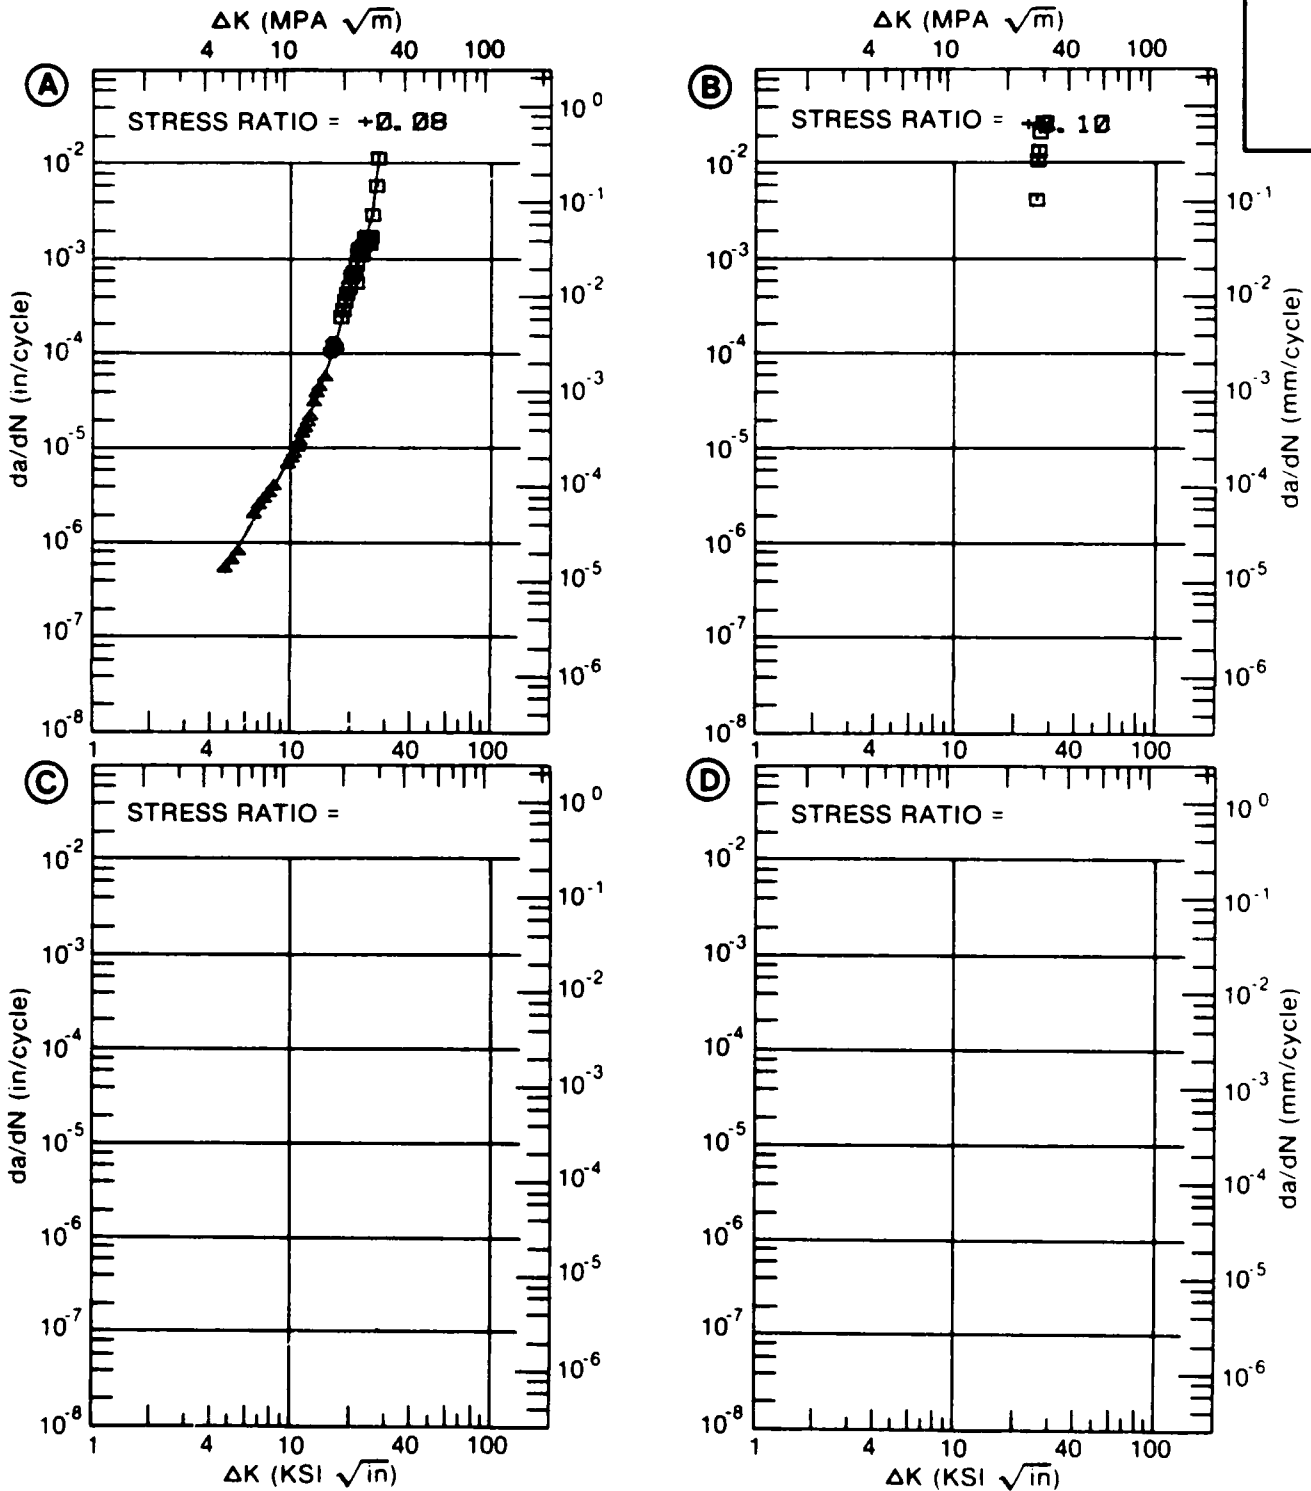


Figure 7.5.3.79

TABLE 7.5.3.80

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.80 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM		2024			
CONDITION: T861					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		F(HZ)= 0.10-0.40	F(HZ)= 1.00-10.00	F(HZ)= 10.00-20.00	
DELTA K	A: 16.87	167.			
MIN	B: 13.66		65.8		
	C: 4.64			.90	
	D:				
	5.00			1.05	
	6.00			1.63	
	7.00			2.57	
	8.00			4.06	
	9.00			6.40	
	10.00			10.0	
	13.00			36.3	
	16.00		175.	121.	
	20.00	696.	642.		
	25.00	6906.			
DELTA K	A: 27.35	22814.			
MAX	B: 20.30		893.		
	C: 17.18			190.	
	D:				
ROOT MEAN SQUARE		28.81	12.20	17.24	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8		1	1	
RATIO	0.8-1.25	2	3	6	
SUMMARY	1.25-2.0	1	1		
(NP/NA)	>2.0				

CONDITION/HT: T861
 FORM: 0.09" TH SHEET
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 73.0 KSI
 ULT. STRENGTH: 76.6 KSI
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

ALUM.
 ALLOY
 2024

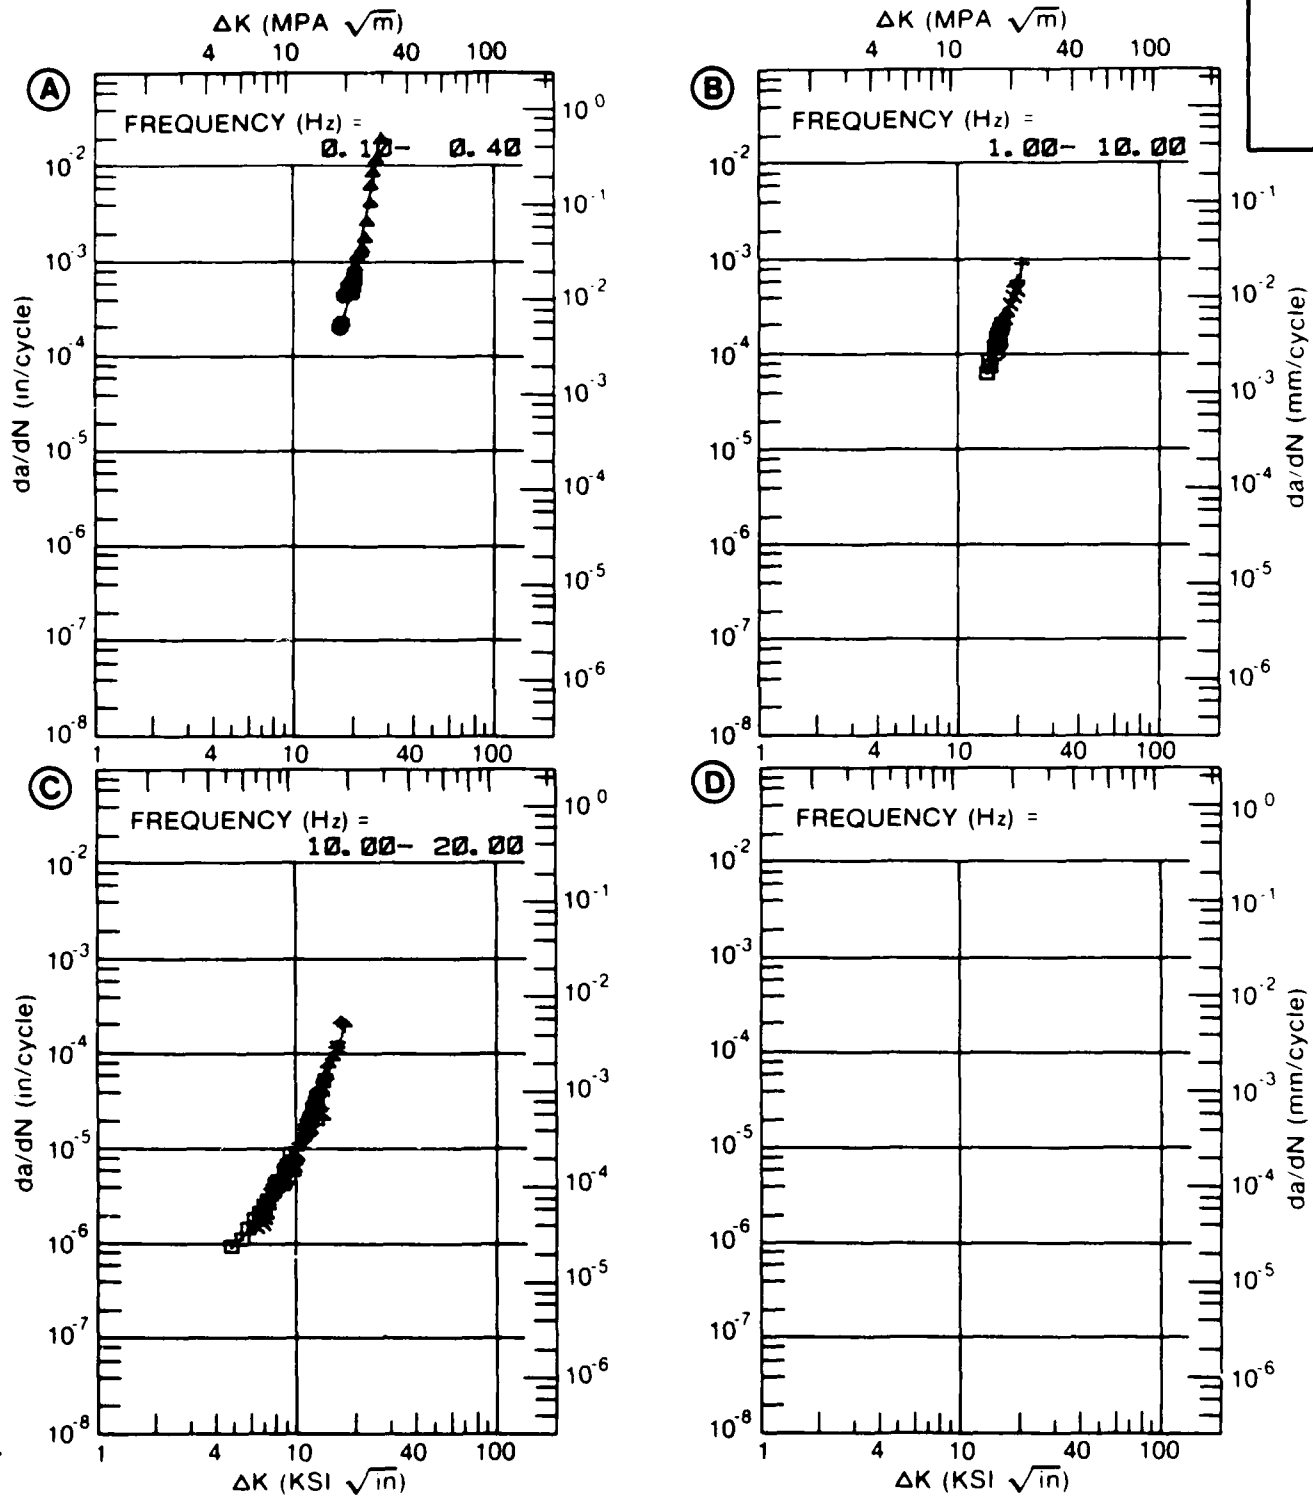


Figure 7.5.3.80

TABLE 7.5.3.81

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.81 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM 2024
CONDITION: T861
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	F(HZ)= 0.10	F(HZ)= 1.00-5.00	F(HZ)= 10.00-15.00	
DELTA K MIN	A: 15.86 : 762.	B: 11.86 : 121.	C: 4.66 : .582	D:
	5.00 :		1.23	
	6.00 :		2.79	
	7.00 :		4.68	
	8.00 :		8.57	
	9.00 :		16.4	
	10.00 :		31.8	
	13.00 :	198.		
	16.00 : 730.			
DELTA K MAX	A: 18.41 : 3233.	B: 15.02 : 536.	C: 10.48 : 43.7	D:

ROOT MEAN SQUARE 25.86 9.54 8.61
PERCENT ERROR

LIFE PREDICTION RATIO SUMMARY (NP/NA)

0.0-0.5			
0.5-0.8			
0.8-1.25	1	1	1
1.25-2.0			
>2.0			

CONDITION/HT: T861
 FORM: 0.09" TH SHEET
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.40
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 73.0 KSI
 ULT. STRENGTH: 76.6 KSI
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

ALUM. ALLOY
2024

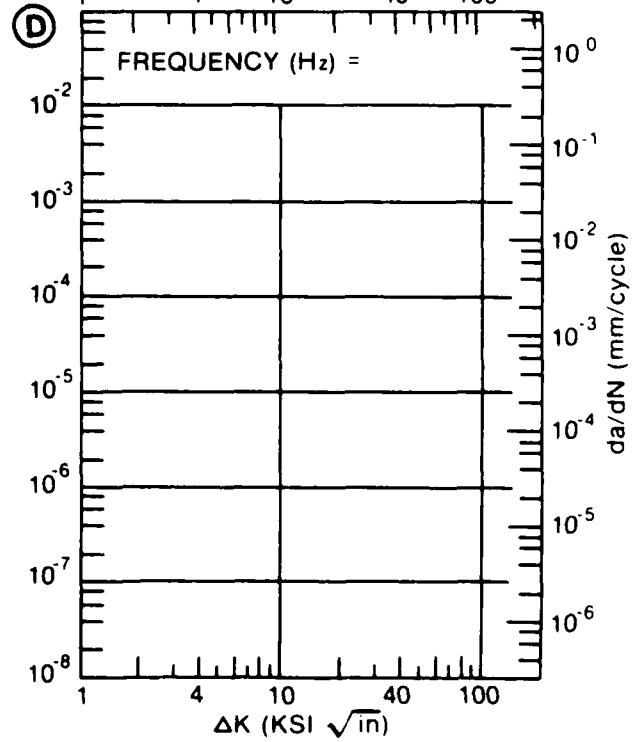
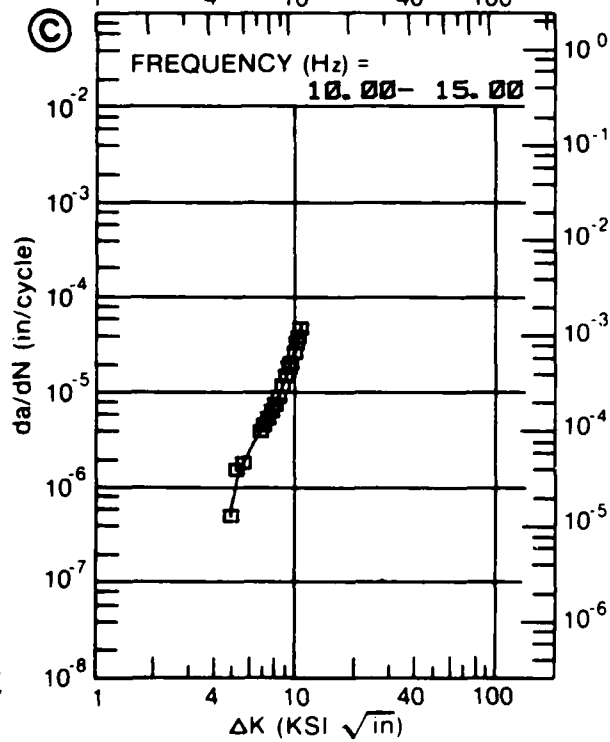
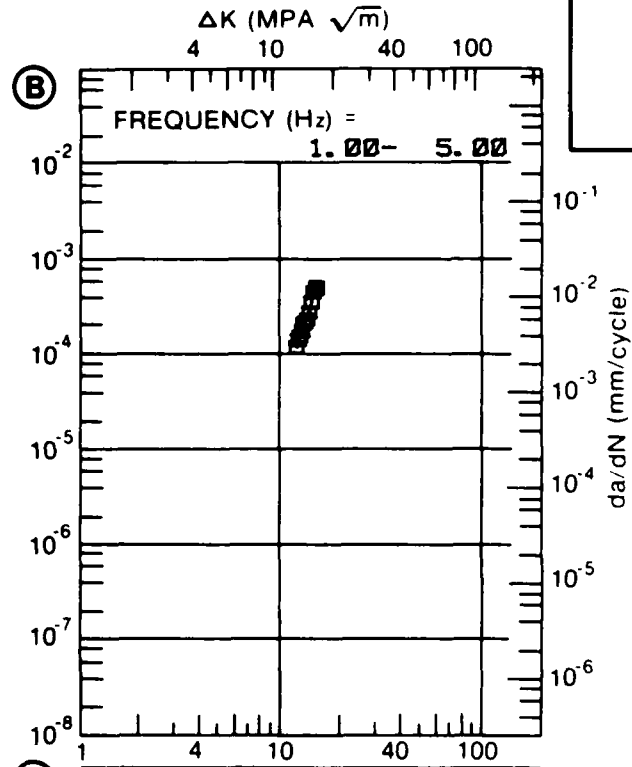
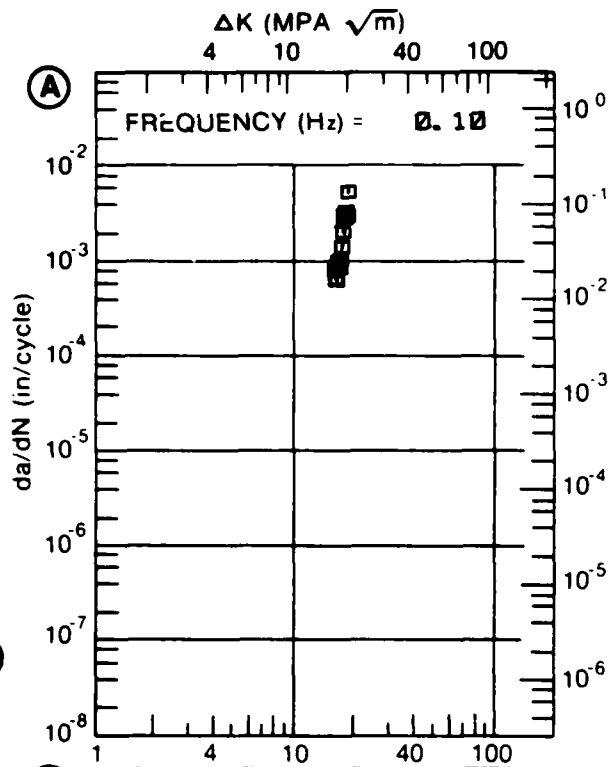


Figure 7.5.3.81

TABLE 7.5.3.82

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.82 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T861
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A:	9.69	6.16		
	B:				
	C:				
	D:				
		10.00	6.91		
		13.00	16.3		
		16.00	45.0		
DELTA K MAX	A:	17.41	84.3		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 16.15
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 4
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T061
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 70.8 KSI
 ULT. STRENGTH: 74.9 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

ALUM.
ALLOY

2024

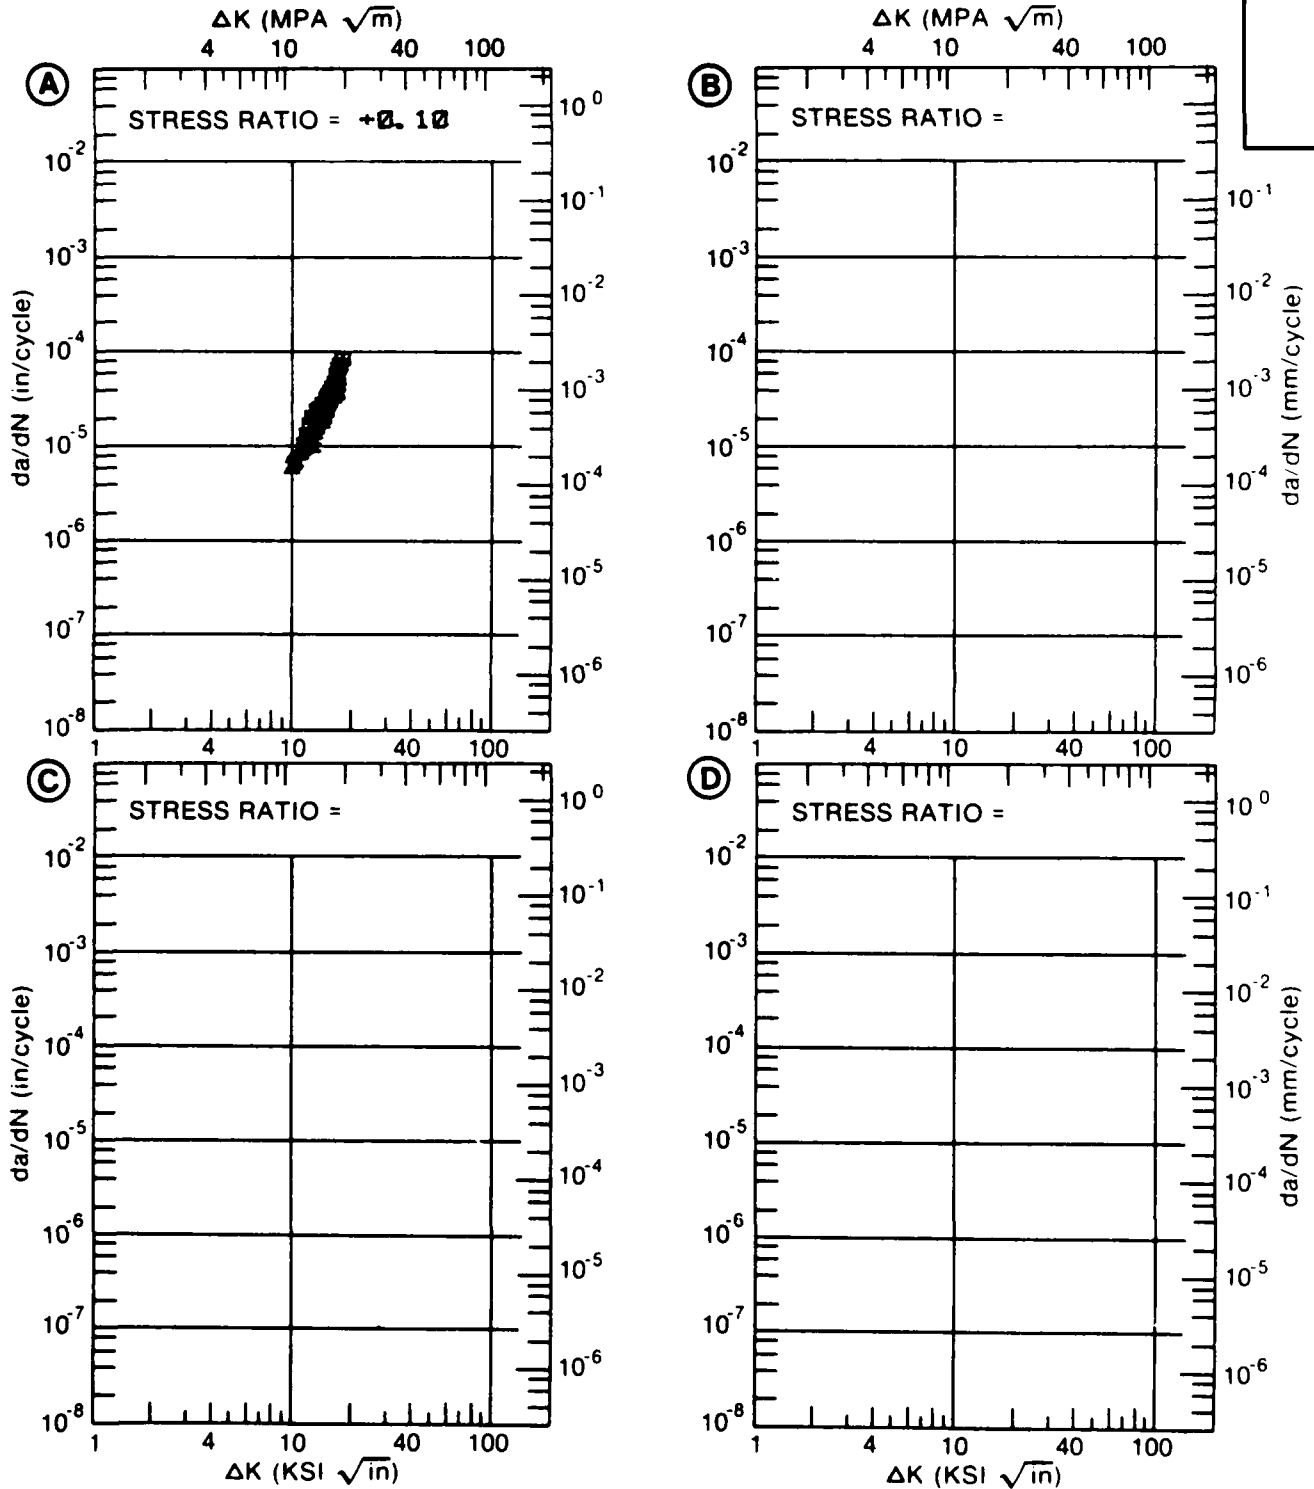


Figure 7.5.3.82

TABLE 7.5.3.83

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.83 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2024			
CONDITION: T861					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.40		
DELTA K	A: 11.03	11.8			
MIN	B:				
	C:				
	D:				
	13.00	17.4			
	16.00	38.5			
	20.00	127.			
	25.00	580.			
	30.00	2479.			
	35.00	9690.			
DELTA K	A: 36.01	12618.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		21.52	0.00		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	3			
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: T881
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.00- 5.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 70.6 KSI
 ULT. STRENGTH: 74.9 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: 88578

ALUM.
ALLOY

2024

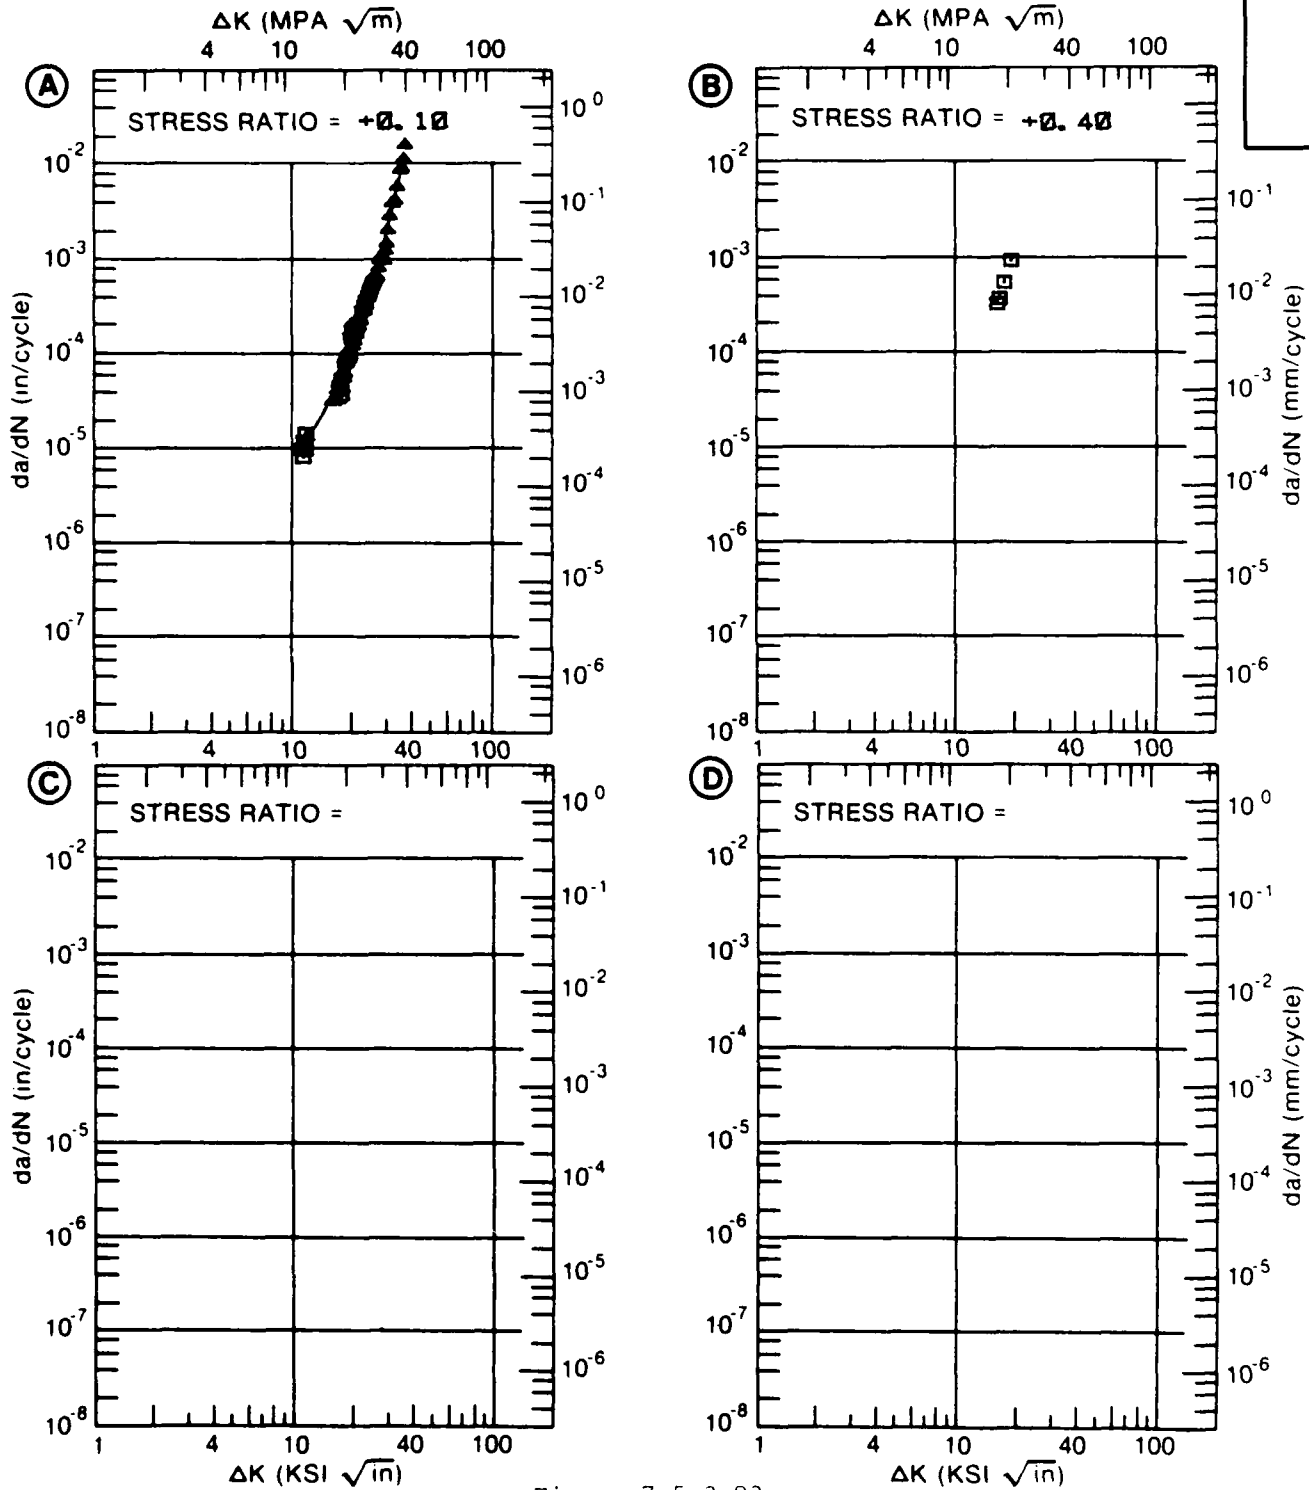


Figure 7.5.3.83

TABLE 7.5.3.84

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.84 INDICATING EFFECT
OF FORM

MATERIAL: ALUMINUM 2024
CONDITION: T351
ENVIRONMENT: 3X/DAY-3.5NACL

K MAX (KSI*IN**1/2)		DA/DT (10**-6 IN/HOUR)			
		A	B	C	D
		T(IN)= 1.0 PLATE	T(IN)= 1.2 PLATE	T(IN)= 2.0 PLATE	
K MAX MIN	A: 14.00 :	826.			
	B: 9.50 :		312.		
	C:				
	D:				
	10.00 :		337.		
	13.00 :		518.		
	16.00 :	875.	743.		
20.00 :	1006.	1087.			
25.00 :	1141.	1535.			
30.00 :	1184.	1947.			
35.00 :	1130.	2278.			
K MAX MAX	A: 40.00 :	1001.			
	B: 39.00 :		2472.		
	C:				
	D:				
ROOT MEAN SQUARE		17.25	2.55	0.00	
PERCENT ERROR					

CONDITION/HT: T351
 ENVIRONMENT: 3X/DAY-3.5NACL
 SPECIMEN TYPE: DCB
 ORIENTATION: S-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 CRACK LENGTH (A₀):
 K_{Isc}:
 REFERENCES: 78313, 84284

ALUM.
 ALLOY
 2024

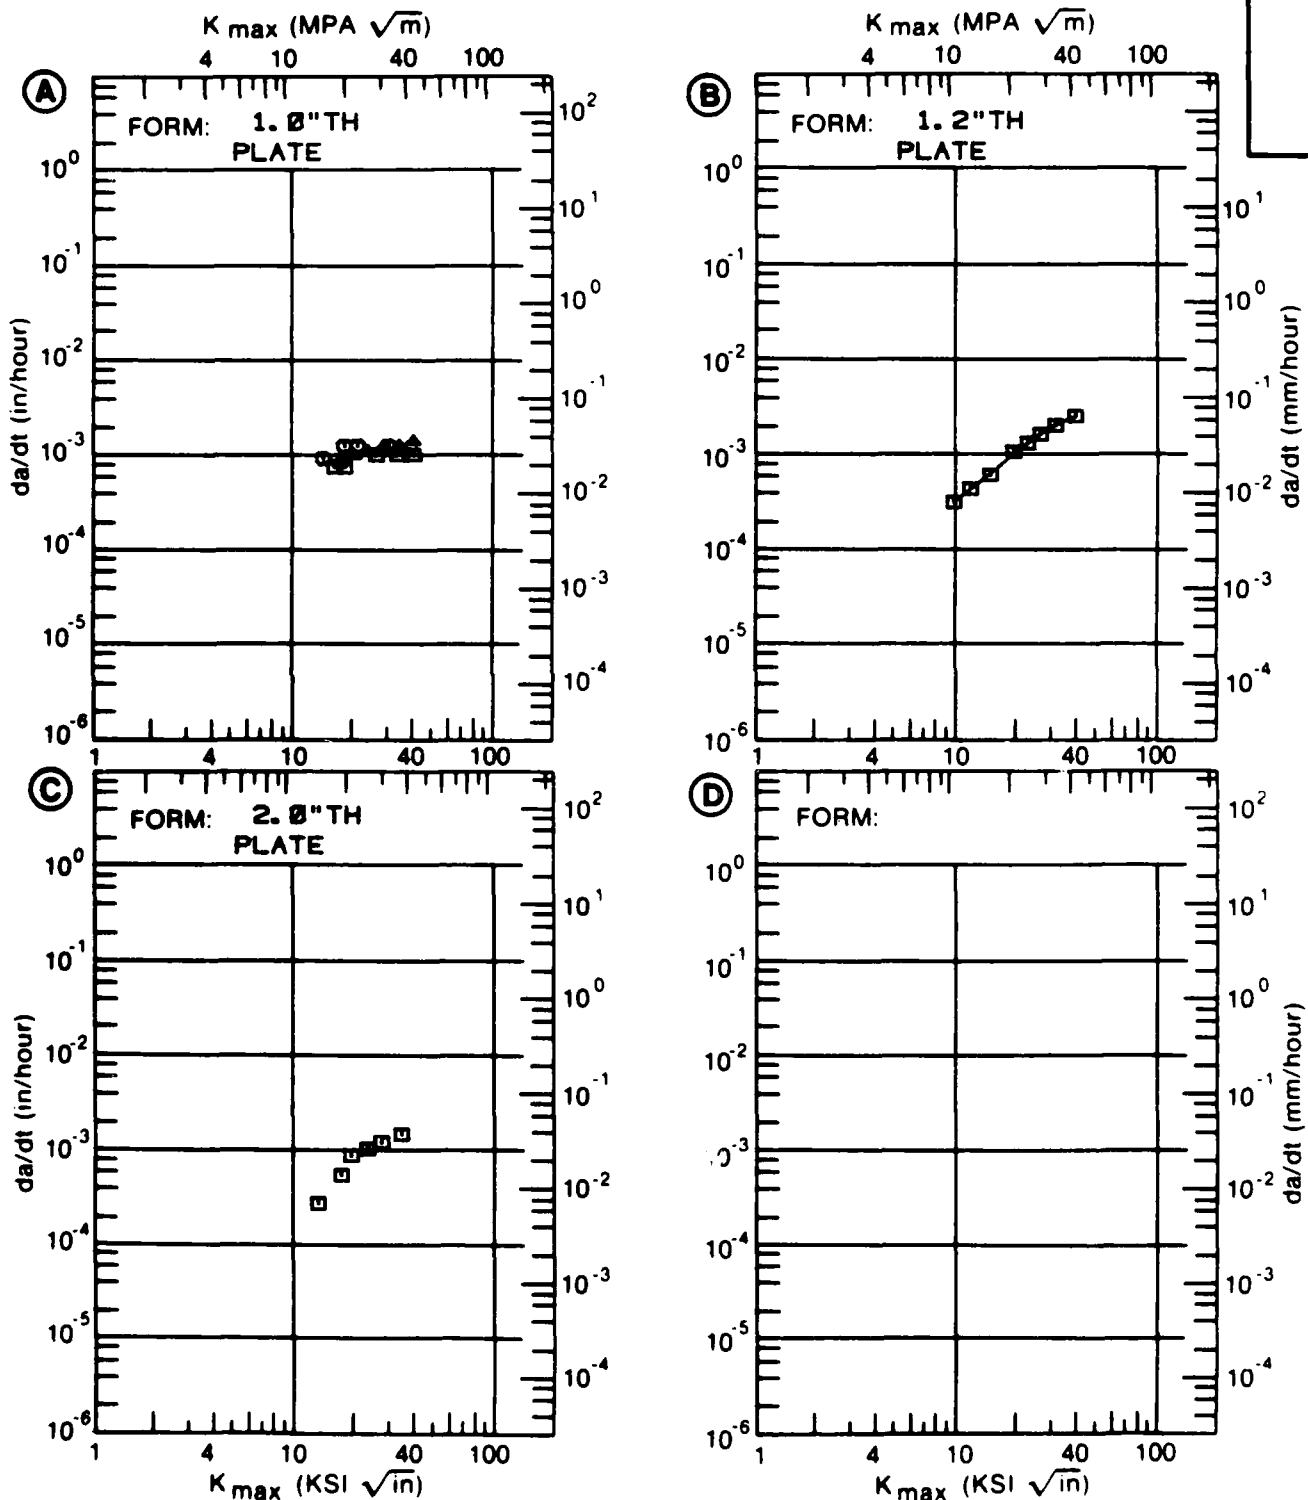


Figure 7.5.3.84

TABLE 7.5.3.85

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.5.3.85 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 2024
CONDITION: T4

K MAX (KSI*IN**1/2)	DA/DT (10**-6 IN/HOUR)			
	A	B	C	D
	E= WET 3X/DAY WITH 3.5% NAACL			
A: 10.00	376.			
B:				
C:				
D:				
13.00	545.			
16.00	654.			
20.00	736.			
25.00	788.			
30.00	822.			
35.00	856.			
40.00	897.			
50.00	1013.			
A: 60.00	1189.			
B:				
C:				
D:				

ROOT MEAN SQUARE 8.21
PERCENT ERROR

CONDITION/HT: T4
 FORM: FORGING
 SPECIMEN TYPE: DCB
 ORIENTATION: S-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 CRACK LENGTH (A_0):
 K_{ISCC} :
 REFERENCES: 78313

ALUM.
 ALLOY

2024

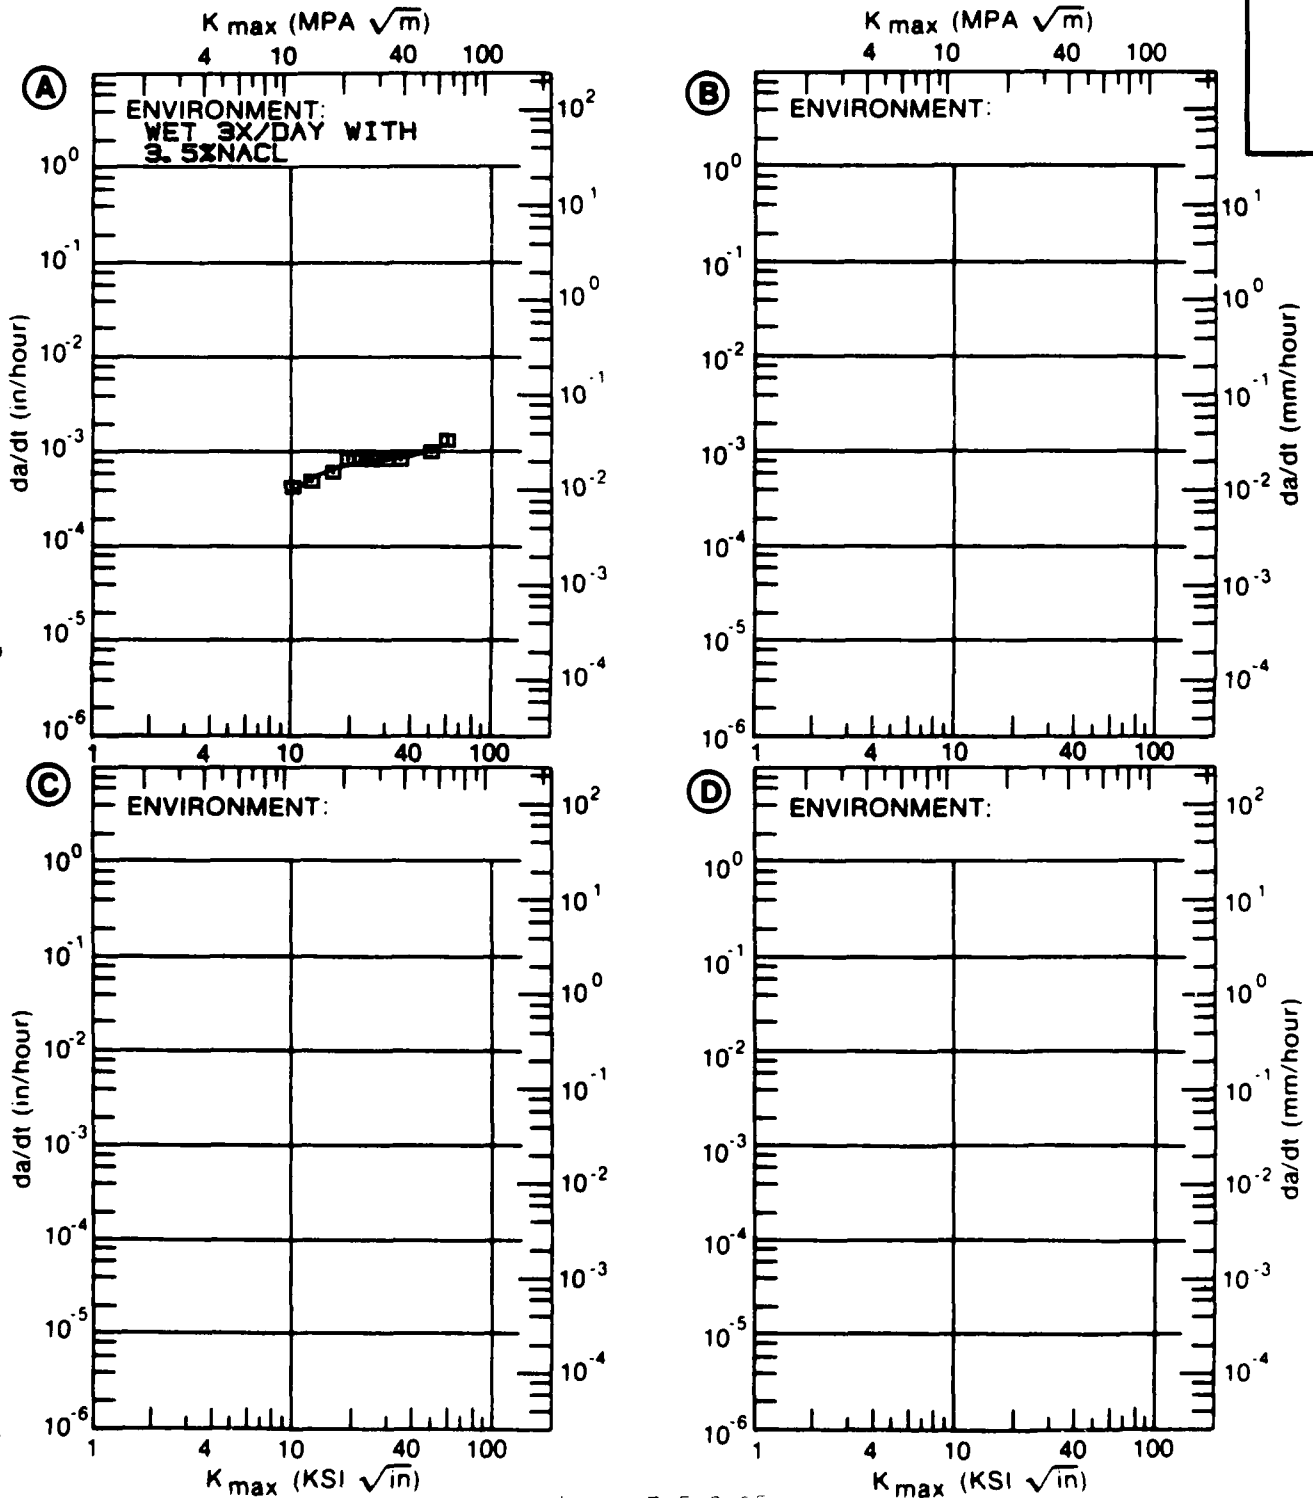


Figure 7.5.3.85

TABLE 7.5.3.86

CONDITION	--PRODUCT--		TEST SPEC OR STR (KSI)	YIELD (F)	ENVIRONMENT	ALUMINUM 2024		K (ISCC)		CRACK LENGTH K (G) (IN) (*SG)	K (ISCC) MEAN (IN) (KBI*SGRT IN)	STAN DEV	TEST TIME (MIN)	DATE REFER		
	FORM	THICK (IN)				WIDTH (IN) W	THICK (IN) B	DESIGN (IN) A	LENGTH (IN) A						K (ISCC)	K (ISCC)
T351	P	2.50	R.T.	S-L	42.4	INDUSTRIAL ATM	2.000	1.000	CT	---	21.20	10.00	---	1973 86688		
T351	P	2.50	R.T.	S-L	42.4	SALT-DICHR-O-MATE-ACETATE	2.000	1.000	CT	---	21.20	9.00	---	1973 86688		
T351	P	2.50	R.T.	S-L	42.4	SEACOAST ATM	2.000	1.000	CT	---	21.20	10.00	---	1973 86688		
T351	P	1.00	R.T.	S-L	47.0	3.5 PCT NAACL	5.000	1.000	DCB	---	90.00	10.00	---	1969 78313		
T352	F	6.00	R.T.	S-L	43.3	SEAWATER	1.400	0.700	DCB	---	27.60	23.00*	---	1972 82675		
T851	P	3.20	R.T.	L-T	59.3	AIR 78PCT RH	5.000	1.250	TDCB	---	18.60	22.70	---	1971 84360		
T851	P	3.20	R.T.	L-T	59.3	DIST WATER	5.000	1.250	TDCB	---	18.60	22.00	---	1971 84360		
T851	P	3.20	R.T.	L-T	59.3	JP-4 FUEL	5.000	1.250	TDCB	---	18.60	21.60	---	1971 84360		
T851	P	3.20	R.T.	L-T	59.3	3.5 PCT NAACL	5.000	1.250	TDCB	---	18.60	21.50	---	1971 84360		
T851	P	2.50	R.T.	S-L	61.8	INDUSTRIAL ATM	2.000	1.000	CT	---	16.70	16.00	---	1973 86688		
T851	P	2.50	R.T.	S-L	61.8	SALT-DICHR-O-MATE-ACETATE	2.000	1.000	CT	---	16.70	15.00	---	1973 86688		
T851	P	2.50	R.T.	S-L	61.8	SEACOAST ATM	2.000	1.000	CT	---	16.70	16.00	---	1973 86688		
T852	F	3.00	R.T.	L-T	53.0	S.C.S.	5.500	1.000	DCB	---	34.00	22.10	64920	1976 R1006		
		3.00			53.0		5.500	1.000	DCB	---	34.00	34.00	61680	1976 R1006		
													28.1 /	8.4		
T852	F	3.00	R.T.	L-T	58.0	S.T.W.	5.500	1.000	DCB	---	37.00	22.50	76140	1976 R1006		
		3.00			58.0		5.500	1.000	DCB	---	37.00	23.50	76140	1976 R1006		
		3.00			58.0		5.500	1.000	DCB	---	37.00	22.50	76140	1976 R1006		
													22.5 /	0.0		

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5 (KISCC/TYS)SQUARED

TABLE 7.5.3.86 (Con't)

CONDITION	--PRODUCT--		TEST TEMP (F)	SPEC OR	YIELD (KSI)	ENVIRONMENT	2024		K (IBCC)	CRACK		MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)					WIDTH (IN)	THICK (IN)		DESIGN (S=SQ)	LENGTH (IN)				
							A	B		A					
T852	F	3.00	R. T.	T-L	94.0	S. T. W	5.500	1.000	DCB	---	34.00	19.80		133680	1976 R1006
T852	F	3.00	R. T.	T-L	54.0	S. T. W.	5.500	1.000	DCB	---	34.00	> 21.00		133680	1976 R1006
		3.00			54.0		5.500	1.000	DCB	---	34.00	> 21.00		133680	1976 R1006
		3.00			54.0		5.500	1.000	DCB	---	34.00	20.90		133680	1976 R1006
T852	F	3.00	R. T.	S-L	---	S. T. W.	5.500	1.000	DCB	---	37.00	20.00		133680	1976 R1006
		3.00			---		5.500	1.000	DCB	---	37.00	> 13.90		133680	1976 R1006
T852	F	6.00	R. T.	S-L	53.9	SEAWATER	1.400	0.700	CANT	---	17.60	14.00		---	1972 82675

TABLE 7.6.2.1

ALUMINUM		2024 (ALCLAD)		K(C)												
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR STR (KSI)	YIELD (KSI)	CRACK LENGTH CROSS STRESS				K(C) STAN MEAN DEV (KSI*SQRT IN)	REFER							
				WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)			ONSET (KSI)	MAX (KSI)					
	H	B	2A(O)	2A(F)	S(O)	S(MAX)										
BUCKLING OF CRACK EDGES RESTRAINED																
T3	S	0.01	R.T.	L-T	51.8	15.000	0.009	7.500	8.890	---	21.20	86.53*	102.53*	1966	86734	
T3	S	0.01	R.T.	L-T	51.8	15.000	0.010	7.500	8.840	---	21.40	87.35*	102.84*	1966	86734	
T3	S	0.02	R.T.	L-T	42.3	15.000	0.019	7.500	9.900	---	21.90	89.39*	121.04*	1966	86734	
T3	S	0.03	R.T.	L-T	53.0	15.000	0.030	7.500	9.600	---	22.30	91.02*	118.30*	1966	86734	
T3	S	0.03	R.T.	L-T	53.0	15.000	0.030	7.500	9.330	---	22.80	93.06*	116.69*	1966	86734	
T3	B	0.04	R.T.	L-T	45.0	11.800	0.039	4.720	6.530	18.10	24.20	73.26*	96.48*	1966	70519	
		0.04			45.0	11.800	0.039	4.720	6.170	17.20	23.90	72.35*	90.15*	1966	70519	
		0.04			45.0	11.800	0.039	3.540	5.240	20.40	29.20	72.95*	95.69*	1966	70519	
		0.04			45.0	11.800	0.039	1.770	2.600	23.60	36.00	60.87*	75.01*	1966	70519	
		0.04			45.0	11.800	0.039	1.770	2.400	30.50	36.20	61.21*	72.14*	1966	70519	
		0.04			45.0	11.800	0.039	1.770	2.950	29.80	36.20	61.21*	81.07*	1966	70519	
		0.04			45.0	11.800	0.039	1.180	1.930	33.80	40.10	54.93*	71.00*	1966	70519	
		0.04			45.0	11.800	0.039	1.180	1.610	35.20	39.80	54.52*	64.03*	1966	70519	
		0.04			45.0	11.800	0.039	3.540	5.150	20.60	29.50	73.70*	95.37*	1966	70519	
T3	S	0.06	R.T.	L-T	52.8	48.000	0.060	24.000	29.850	---	19.10	139.46	174.83*	1966	86734	
		0.06			52.8	48.000	0.061	24.000	28.250	---	19.60	143.11	141.3/ 2.6	168.24*	1966	86734
T3	S	0.08	R.T.	L-T	50.1	5.900	0.079	1.580	1.890	31.90	37.30	61.50*	68.66*	1966	84366	
		0.08			50.1	5.900	0.079	1.580	1.890	32.60	37.30	61.50*	68.66*	1966	84366	
		0.08			50.1	5.900	0.079	1.180	---	---	41.20	57.52*	---	1966	84366	
		0.08			50.1	5.900	0.079	0.790	1.020	43.00	46.00	51.82*	59.32*	1966	84366	
		0.08			50.1	5.900	0.079	0.790	---	---	42.30	46.10	51.93*	---	1966	84366
		0.08			50.1	5.900	0.079	3.150	3.540	19.40	22.50	61.21*	69.20*	1966	84366	
		0.08			50.1	5.900	0.079	3.150	3.460	17.60	22.10	60.13*	66.25*	1966	84366	
		0.08			50.1	5.900	0.079	1.180	1.380	35.60	41.20	57.52*	62.79*	1966	84366	
		0.08			50.1	5.900	0.079	0.790	0.980	42.70	45.90	51.70*	57.74*	1966	84366	
		0.08			50.1	5.900	0.079	1.580	2.120	---	37.30	61.50*	74.05*	1966	84366	
		0.08			50.4	5.900	0.079	0.790	1.140	---	43.70	49.23*	59.86*	1966	84366	
		0.08			50.4	5.900	0.079	1.580	2.120	---	36.00	59.36*	71.47*	1966	84366	
		0.08			50.4	5.900	0.079	0.790	1.220	40.30	43.90	49.45*	62.43*	1966	84366	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 7.6.2.1 (Con't)

ALUMINUM		2024 (ALCLAD)		K(C)									
CONDITION	---PRODUCT--- FORM THICK TEMP OR (IN) (F)	YIELD STR (KSI)	CRACK LENGTH GROSS STRESS				K(APP) STAN		K(C) STAN				
			WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	MEAN (KSI)	DEV (KSI)	MEAN (KSI)	DEV (KSI)	
			W	B	2A(D)	2A(F)	S(D)	S(MAX)	(KBI)	(KBI)	(KBI)	(KBI)	REFER
T3	S	50.4	0.08	R.T.	L-T	50.4	0.079	1.580	2.010	33.30	36.20	59.69*	1966 84366
		50.4	0.08			50.4	0.079	3.150	3.540	15.90	21.40	58.22*	1966 84366
		50.4	0.08			50.4	0.079	1.180	1.610	36.70	40.30	58.22*	1966 84366
		50.4	0.08			50.4	0.079	1.180	1.500	36.60	40.10	55.98*	1966 84366
		50.4	0.08			50.4	0.079	1.180	1.610	35.20	39.80	55.56*	1966 84366
		50.4	0.08			50.4	0.079	1.580	2.120	30.80	35.90	59.20*	1966 84366
		50.4	0.08			50.4	0.079	0.790	1.180	39.30	43.10	48.59*	1966 84366
		51.8	0.08			51.8	0.079	1.180	1.580	34.60	40.90	57.10*	1966 84366
		51.8	0.08			51.8	0.079	0.790	1.220	45.30	46.20	52.04*	1965 70485
		51.8	0.08			51.8	0.079	0.790	1.140	43.10	44.00	49.56*	1965 70485
		51.8	0.08			51.8	0.079	3.150	3.500	19.60	20.50	55.77*	1966 84366
		51.8	0.08			51.8	0.079	1.180	1.530	33.60	41.10	57.38*	1966 84366
		51.8	0.08			51.8	0.079	0.390	0.630	49.50	50.00	39.24*	1965 70485
		51.8	0.08			51.8	0.079	0.790	1.140	43.10	44.00	49.56*	1966 84366
		51.8	0.08			51.8	0.079	3.150	3.500	19.60	20.50	55.77*	1965 70485
		51.8	0.08			51.8	0.079	1.580	2.160	31.20	36.60	60.35*	1966 84366
		51.8	0.08			51.8	0.079	1.580	2.050	29.60	37.00	61.01*	1965 70485
		51.8	0.08			51.8	0.079	0.790	1.220	45.30	46.20	52.04*	1966 84366
		51.8	0.08			51.8	0.079	0.790	1.140	46.30	46.90	52.83*	1965 70485
		51.8	0.08			51.8	0.079	3.150	3.500	20.20	21.20	57.68*	1965 70485
	51.8	0.08			51.8	0.079	3.150	3.580	20.60	21.30	57.95*	1965 70485	
	51.8	0.08			51.8	0.079	0.790	1.140	46.30	46.90	52.83*	1966 84366	
	51.8	0.08			51.8	0.079	1.180	1.500	36.10	41.10	57.38*	1966 84366	
	51.8	0.08			51.8	0.079	3.150	3.500	33.40	36.60	60.35*	1965 70485	
	51.8	0.08			51.8	0.079	0.390	0.670	49.10	49.40	38.77*	1966 84366	
	51.8	0.08			51.8	0.079	1.580	2.080	33.40	36.60	60.35*	1966 84366	
	53.0	0.08			53.0	0.079	1.180	1.650	37.20	40.90	56.82*	1966 84366	
	53.0	0.08			53.0	0.079	1.180	1.580	36.40	40.90	57.10*	1966 84366	
	53.0	0.08			53.0	0.079	0.790	1.140	---	45.00	50.69*	1966 84366	
	53.0	0.08			53.0	0.079	1.180	1.610	36.60	40.00	55.84*	1966 84366	

BUCKLING OF CRACK EDGES RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

ALUMINUM		2024 (ALCLAD)		K(C)		CRACK LENGTH GROSS STRESS															
CONDITION	--PRODUCT-- FORM	THICK (IN)	SPECIMEN W	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K (APP) (KSI*SQRT IN)	STAN DEV	K (C) (KSI*SQRT IN)	MEAN DEV	STAN DEV	K (C) (KSI*SQRT IN)	MEAN DEV	DATE	REFER				
																		2A(O)	2A(F)	S(O)	S(MAX)
T3	S	0.08	R. T.	L-T	53.0	0.079	0.790	---	45.00	50.69*	---	---	---	---	---	---	---	1966 84366			
					53.0	0.079	3.150	3.420	21.80	59.31*	68.83*	---	---	---	---	---	---	---	---	1966 84366	
					53.0	0.079	0.790	---	44.90	50.58*	---	---	---	---	---	---	---	---	---	---	1966 84366
					53.0	0.079	1.580	2.090	37.70	62.16*	73.18*	---	---	---	---	---	---	---	---	---	1966 84366
					53.0	0.079	3.150	3.980	---	21.10	57.41*	65.75*	---	---	---	---	---	---	---	---	1966 84366
					53.0	0.079	1.580	1.970	29.00	36.20	59.69*	68.45*	---	---	---	---	---	---	---	---	1966 84366
					53.0	0.079	1.580	2.120	30.70	35.20	58.04*	69.88*	---	---	---	---	---	---	---	---	1966 84366
					51.8	0.079	1.770	2.480	30.50	41.90	70.83*	85.03*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.180	1.580	31.00	45.10	61.78*	71.85*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.770	2.280	28.50	42.10	71.19*	81.56*	---	---	---	---	---	---	---	---	1965 70485
T3	S	0.08	R. T.	L-T	51.8	0.079	4.720	5.830	17.40	28.50	86.28*	102.09*	---	---	---	---	---	---	1965 70485		
					51.8	0.079	3.540	4.540	24.90	34.00	84.94*	100.09*	---	---	---	---	---	---	---	1965 70485	
					51.8	0.079	3.540	4.610	25.80	33.80	84.44*	100.59*	---	---	---	---	---	---	---	1965 70485	
					51.8	0.079	4.720	5.710	17.20	28.30	85.67*	99.56*	---	---	---	---	---	---	---	1965 70485	
					51.8	0.079	1.180	1.610	33.40	45.80	62.74*	73.68*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.770	2.480	32.30	42.10	71.19*	85.43*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.180	2.240	32.00	45.50	62.33*	87.30*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.180	2.620	37.80	49.20	67.09*	100.58*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	3.150	4.450	25.60	35.40	79.62*	95.70*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.580	---	---	46.30	73.14*	---	---	---	---	---	---	---	---	---	1965 70485
T3	S	0.08	R. T.	L-T	51.8	0.079	1.580	2.520	40.70	48.60	76.78*	97.38*	---	---	---	---	---	---	1965 70485		
					51.8	0.079	4.720	5.750	22.20	29.80	83.20*	92.99*	---	---	---	---	---	---	---	1965 70485	
					51.8	0.079	6.300	9.450	18.00	30.90	101.71*	132.39*	---	---	---	---	---	---	---	1965 70485	
					51.8	0.079	8.660	11.720	13.20	25.20	101.50*	128.24*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	15.750	---	---	13.70	96.46*	---	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.580	2.440	40.71	47.00	74.23*	92.62*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	3.150	4.490	25.30	37.00	83.23*	100.51*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.180	1.850	41.90	4.50	66.13*	82.99*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	3.150	4.600	28.00	34.60	77.82*	95.25*	---	---	---	---	---	---	---	---	1965 70485
					51.8	0.079	1.180	2.090	41.70	50.00	68.18*	71.04*	---	---	---	---	---	---	---	---	1965 70485
T3	S	0.08	R. T.	L-T	51.8	0.079	0.790	1.420	28.90	52.40	58.41*	78.43*	---	---	---	---	---	1965 70485			
					51.8	0.079	0.790	1.690	46.20	50.40	56.18*	82.38*	---	---	---	---	---	---	---	1965 70485	
T3	S	0.08	R. T.	L-T	51.8	0.079	4.720	7.400	23.90	37.80	105.54*	137.29*	---	---	---	---	1965 70485				

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

ALUMINUM		2024 (ALCLAD)		K(C)		CRACK LENGTH		GROSS STRESS		K(AFF) STAN		K(C) STAN												
CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR	YIELD STR (KSI)	---SPECIMEN---		INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(AFF) (KSI*SQRT IN)	MEAN (IN)	DEV (KSI*SQRT IN)	K(C) (KSI*SQRT IN)	MEAN (IN)	DEV (KSI*SQRT IN)	DATE	REFER						
					WIDTH (IN)	THICK (IN)																		
T3	S	0.08	R. T.	L-T	51.8	23.600	0.079	1.970	3.190	32.60	45.10	79.68*			102.11*				1965	70485				
					51.8	23.600	0.079	4.300	9.050	15.90	31.90	105.00*					132.30*				1965	70485		
					51.8	23.600	0.079	11.800	12.320	12.70	20.20	103.42					109.24*				1965	70485		
					51.8	23.600	0.079	4.720	6.300	23.60	31.30	87.39					103.03*				1965	70485		
					51.8	23.600	0.079	0.790			49.80	55.51*	89.9/10.5						1965	70485				
T3	S	0.09	R. T.	L-T	56.0	5.900	0.095	0.750	1.060	46.40	47.60	53.62*			62.67*					1966	84366			
					56.0	5.900	0.095	1.580	2.240	25.80	38.20	62.99*					78.78*				1966	84366		
					56.0	5.900	0.095	1.580	2.400	31.80	38.20	62.99*					82.78*				1966	84366		
					56.0	5.900	0.095	3.150	3.900	20.30	23.80	64.73*					72.26*				1966	84366		
					56.0	5.900	0.095	3.150	3.740	21.60	23.60	64.21*					77.56*				1966	84366		
					56.0	5.900	0.095	0.790	1.100	46.40	47.90	53.51*					63.81*					1966	84366	
					56.0	5.900	0.095	1.180	1.540	39.80	43.00	60.03*					69.84*					1966	84366	
					53.2	11.800	0.118	3.540	4.690	23.30	32.20	80.44*					97.03*					1966	70319	
					53.2	11.800	0.118	1.770	2.520	34.00	41.90	70.17*					84.97*					1966	70319	
T3	S	0.11	R. T.	L-T	53.2	11.800	0.118	1.770	2.720	31.90	41.60	70.34*			88.92*					1966	70319			
					53.2	11.800	0.118	1.770	2.480	35.70	41.90	70.85*				85.03*					1966	70319		
					53.2	11.800	0.118	4.720	3.400	20.40	25.60	77.50*				85.95*					1966	70319		
					53.2	11.800	0.118	4.720	3.950	20.60	25.20	76.29				86.54*						1966	70319	
					53.2	11.800	0.118	1.180	1.730	38.70	45.00	61.65*				75.18*						1966	70319	
					53.2	11.800	0.118	3.540	4.560	25.20	32.20	80.44*				95.09*						1966	70319	
					53.2	11.800	0.118	1.180	1.810	37.80	44.30	60.69*				75.80*							1966	70319
					52.0	11.800	0.158	1.770	2.990	34.80	41.10	69.50*				92.77*							1966	70319
					52.0	11.800	0.158	3.540	4.210	23.30	32.20	80.44*				89.97*							1966	70319
					52.0	11.800	0.158	4.720	3.640	20.90	26.50	80.22*				92.24*							1966	70319
					T3	S	0.16	R. T.	L-T	52.0	11.800	0.158	1.180	1.610	38.10	44.30	60.69*			71.27*				
52.0	11.800	0.158	3.540	4.610						26.30	32.50	81.19*			96.72*							1966	70319	
52.0	11.800	0.158	4.720	6.060						19.80	26.90	81.43*			99.78*								1966	70319
52.0	11.800	0.158	1.180	1.610						38.40	44.40	60.82*			71.43*								1966	70319
52.0	11.800	0.158	1.770	2.440						33.80	41.60	70.34*			83.66*								1966	70319
52.0	11.800	0.158	1.770	2.520						34.00	41.30	69.84*			84.56*								1966	70319
T3	S	0.01	R. T.	T-L	46.0	14.990	0.009	7.500	9.510	---	20.80	84.92*							1962	62308				

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

ALUMINUM		2024 (ALCLAD)		K(C)		CRACK LENGTH ORDBS STRESS											
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	---SPECIMEN---		INIT		FINAL		ONSET		MAX		K(APP) STAN		K(C) STAN	
				WIDTH (IN)	THICK (IN)	(IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)	(KSI)
BUCKLING OF CRACK EDGES RESTRAINED																	
T3	S	0.01	R.T.	T-L	46.0	14.990	0.010	7.500	9.060	---	21.20	86.56*	104.82*	1962	62308	1966	86734
T3	S	0.02	R.T.	T-L	46.5	15.000	0.020	7.500	8.680	---	20.40	83.27*	96.09*	1966	86734	1966	86734
T3	S	0.06	R.T.	T-L	44.9	48.000	0.061	24.000	28.650	---	17.10	124.86	149.12*	1966	86734	1966	86734
T3	S	0.08	R.T.	T-L	43.0	47.980	0.079	24.000	27.150	---	18.80	137.29*	154.64*	1966	86734	1966	86734
T3	S	0.08	R.T.	T-L	43.0	47.980	0.080	24.000	27.810	---	18.90	138.02*	159.50*	1966	86734	1966	86734
BUCKLING OF CRACK EDGES NOT RESTRAINED																	
T3	S	0.06	60	L-T	47.0	12.000	0.061	3.000	---	---	31.60	71.37*	---	1966	86734	1966	86734
T3	S	0.06	60	L-T	47.0	12.000	0.061	3.000	---	---	26.82	71.18*	---	1966	86734	1966	86734
T3	S	0.06	60	L-T	47.0	12.000	0.061	3.000	---	---	32.10	72.90*	---	1966	86734	1966	86734
T3	S	0.03	R.T.	L-T	51.0	9.000	0.032	2.560	2.800	---	31.90	67.36*	71.20*	1965	62311	1966	86734
T3	S	0.04	R.T.	L-T	44.3	7.500	0.040	3.000	---	---	21.30	51.41*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	44.4	7.500	0.040	3.000	---	---	21.90	52.85*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	1.050	---	---	37.20	48.36*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	4.700	---	---	12.14	44.34	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	4.150	---	---	15.27	48.93	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	2.000	---	---	29.90	55.45*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	4.700	---	---	12.14	44.34	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	0.550	---	---	41.30	38.52*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	1.100	---	---	39.60	52.76*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	3.900	---	---	16.73	50.05	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	1.050	---	---	37.10	48.23*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	2.100	---	---	28.70	54.80*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	0.950	---	---	41.60	38.79*	---	1966	86734	1966	86734
T3	S	0.04	R.T.	L-T	46.1	7.500	0.040	0.500	---	---	42.10	37.41*	---	1966	86734	1966	86734

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

ALUMINUM		2024 (ALCLAD)		K(C)																
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	CRACK LENGTH CROSS STRESS		K (APP) STAN MEAN DEV (KSI*SQRT IN)	K (C) STAN MEAN DEV (KSI*SQRT IN)	DATE REFER												
				WIDTH (IN)	THICK (IN)				INIT (IN)	FINAL ONSET (KSI)	MAX (KSI)									
T3	S	R. T.	L-T	47.4	0.04	7.500	0.040	4.700	13.00	47.48	50.83	47.48	50.83	1966	86734					
																47.4	0.040	4.200	15.80	50.83
																47.4	0.040	4.100	16.20	50.86
																47.4	0.040	0.950	42.40	52.31*
																47.4	0.040	0.500	44.90	39.90*
																47.4	0.040	2.200	30.70	60.30*
																47.4	0.040	0.750	43.40	47.40*
																47.4	0.040	4.000	17.33	53.10
																47.4	0.040	2.000	32.90	61.01*
																47.4	0.040	1.050	41.90	54.47*
																47.4	0.040	0.500	45.40	40.35*
																51.0	0.040	1.150	43.90	59.87*
																51.0	0.040	5.900	12.14	64.45*
																51.0	0.040	1.150	44.10	60.13*
																51.0	0.040	0.650	50.70	51.47*
																51.0	0.040	4.280	14.80	48.56
																51.0	0.040	0.810	48.70	55.33*
																51.0	0.040	4.120	17.00	53.63
																51.0	0.040	0.500	51.30	45.99*
																51.0	0.040	4.870	12.14	46.41
51.0	0.040	0.500	51.70	45.74*																
51.0	0.040	1.950	31.40	57.36*																
51.2	0.040	3.000	22.00	53.10																
51.5	0.040	3.000	24.70	59.61																
51.5	0.040	3.000	23.30	56.23																
T3	S	R. T.	L-T	51.0	0.040	9.000	0.040	4.420	4.880	18.10	20.50	63.80	69.93*	1965	62311					
																51.0	0.040	6.300	9.60	9.90
T3	S	R. T.	L-T	51.0	0.040	20.000	0.040	2.260	4.900	27.50	40.10	76.15*	115.56*	1965	62311					
																51.0	0.040	2.260	7.370	27.00

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 7.6.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPEC OR	YIELD STR (KSI)	--SPECIMEN--		CRACK LENGTH CROSS STRESS				K(ALCLAD)		K(C)		K(C) STAN	K(C) MEAN DEV (KSI*SQRT IN)	K(C) STAN	K(C) MEAN DEV (KSI*SQRT IN)	DATE REFER	
	FORM	THICK (IN)			THICK (IN)	WIDTH (IN)	B	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	K(ALCLAD)	K(C)						K(C)
T3	S	0.04	R. T.	L-T	50.6	30.000	0.040	15.000	17.700	---	17.70	102.17	---	137.40*	---	---	---	---	1966 86734	
		0.04			50.6	30.000	0.040	15.000	17.700	---	18.30	105.64	---	124.53*	---	---	---	---	1966 86734	
		0.04			50.9	30.000	0.040	6.000	---	---	27.80	87.51	---	---	---	---	---	---	1966 86734	
		0.04			51.3	30.000	0.040	12.000	---	---	17.50	84.47	---	---	---	---	---	---	1966 86734	
		0.04			51.6	30.000	0.040	12.000	---	---	17.41	84.04	---	---	---	---	---	---	1966 86734	
		0.04			52.1	30.000	0.040	3.000	---	---	36.10	78.85	90.4/10.8	---	---	---	---	---	1966 86734	
T3	S	0.06	R. T.	L-T	53.2	2.000	0.064	0.621	0.980	31.60	36.20	38.00*	---	53.00*	---	---	---	---	1973 86213	
		0.06			53.2	2.000	0.064	0.622	1.020	33.30	36.20	38.08*	---	54.93*	---	---	---	---	1973 86213	
T3	S	0.06	R. T.	L-T	44.2	7.500	0.064	3.760	---	---	19.75	57.14*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	1.080	---	---	41.80	55.15*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	3.910	---	---	18.83	56.47*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	4.900	---	---	12.13	46.76	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	1.940	---	---	34.30	62.47*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	0.500	---	---	44.80	39.81*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	0.960	---	---	45.80	56.82*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	0.500	---	---	46.00	40.88*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	5.450	---	---	12.13	55.01*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	0.500	---	---	45.20	40.17*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	0.500	---	---	46.10	40.97*	---	---	---	---	---	---	1966 86734	
		0.06			44.2	7.500	0.064	1.930	---	---	34.10	61.92*	---	---	---	---	---	---	1966 86734	
T3	S	0.06	R. T.	L-T	52.7	15.810	0.065	3.000	4.370	---	36.10	80.15*	---	99.30*	---	---	---	---	1973 86213	
		0.06			52.7	15.810	0.064	6.010	7.310	---	22.80	77.04	---	89.35*	---	---	---	---	1973 86213	
		0.06			52.7	15.820	0.062	4.000	---	---	30.90	80.66	---	---	---	---	---	---	1973 86213	
	0.06			52.7	15.820	0.063	1.020	1.500	---	47.10	59.77*	78.9/ 2.6	72.70*	---	---	---	---	1973 86213		
T3	S	0.08	R. T.	L-T	49.4	47.990	0.079	24.000	27.300	---	19.60	143.12	143.1/ 0.0	162.14*	---	---	---	---	1966 86734	
		0.08			49.4	47.990	0.080	24.000	27.450	---	19.60	143.12	143.1/ 0.0	163.08*	---	---	---	---	1966 86734	
T3	S	0.09	R. T.	L-T	51.0	9.000	0.091	4.480	4.860	20.10	23.20	73.06*	---	78.82*	---	---	---	---	1965 62311	
		0.09			51.0	9.000	0.091	2.500	3.040	28.10	34.90	72.65*	---	82.12*	---	---	---	1965 62311		
		0.09			51.0	9.000	0.091	4.480	5.060	20.10	23.10	72.75*	---	81.74*	---	---	---	1965 62311		
		0.09			51.0	9.000	0.091	2.560	2.920	28.10	35.70	75.38*	---	81.83*	---	---	---	1965 62311		

*NOTE-- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

ALUMINUM		2024 (ALCLAD)		K(C)		CRACK LENGTH CROSS STRESS				K(AFP) STAN		K(C) STAN				
CONDITION	--PRODUCT-- FORM THICK TEMP OR (IN) (F)	YIELD STR (KSI)	SPECIMEN-- WIDTH (IN)	THICK (IN)	B	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(AFP) (KSI*SQRT IN)	MEAN DEV	STAN DEV	K(C) (KSI*SQRT IN)	MEAN DEV	DATE	REFER
T3	S 0.09 R.T. L-T	51.0	9.000	0.091	0.091	6.230	6.520	10.90	14.00	64.24*	---	---	69.18*	---	---	1965 62311
	0.09	51.0	9.000	0.091	0.091	6.190	6.690	11.00	13.60	61.79*	---	---	69.61*	---	---	1965 62311
T3	S 0.10 R.T. L-T	51.0	9.000	0.102	0.102	2.100	2.340	32.10	36.10	67.86*	---	---	72.25*	---	---	1965 62311
	0.10	51.0	9.000	0.102	0.102	1.700	---	---	39.20	---	---	---	65.80*	---	---	1965 62311
T3	S 0.10 R.T. L-T	52.7	35.000	0.102	0.102	17.850	---	---	13.60	86.33	---	---	---	---	---	1956 84367
	0.10	52.7	35.000	0.102	0.102	1.480	---	---	48.10	73.42*	---	---	---	---	---	1956 84367
	0.10	52.7	35.000	0.102	0.102	4.950	---	---	37.40	103.99*	---	---	---	---	---	1956 84367
	0.10	52.7	35.000	0.102	0.102	17.900	---	---	19.10	121.55	---	---	---	---	---	1956 84367
	0.10	52.7	35.000	0.102	0.102	1.070	---	---	49.60	64.34*	---	---	---	---	---	1956 84367
	0.10	52.7	35.000	0.102	0.102	10.700	---	---	23.60	102.74	103.5/17.6	---	---	---	---	1956 84367
T3	S 0.09 82 L-T	51.2	3.000	0.092	0.092	1.180	2.149	---	31.00	46.75*	---	---	86.69*	---	---	1973 86213
	0.09	51.2	3.000	0.092	0.092	1.230	2.229	---	30.10	46.79*	---	---	89.79*	---	---	1973 86213
	0.09	51.2	3.000	0.092	0.092	1.240	2.103	---	30.00	46.91*	---	---	80.99*	---	---	1973 86213
	0.09	52.0	3.000	0.091	0.091	1.280	2.135	---	29.60	47.41*	---	---	81.98*	---	---	1973 86213
	0.09	52.0	3.000	0.091	0.091	1.200	2.067	---	30.50	46.56*	---	---	80.16*	---	---	1973 86213
	0.09	52.0	3.000	0.092	0.092	1.270	2.164	---	29.30	45.65*	---	---	82.97*	---	---	1973 86213
	0.09	52.5	3.000	0.090	0.090	1.270	2.182	---	29.70	47.29*	---	---	85.32*	---	---	1973 86213
	0.09	52.5	3.000	0.090	0.090	1.330	2.240	---	28.60	46.92*	---	---	86.18*	---	---	1973 86213
	0.09	52.5	3.000	0.091	0.091	1.140	2.067	---	32.30	47.53*	---	---	84.89*	---	---	1973 86213
T3	S 0.02 R.T. T-L	46.5	15.000	0.020	0.020	7.500	9.350	---	19.80	80.82*	---	---	101.60*	---	---	1966 86734
T3	S 0.03 R.T. T-L	44.4	15.010	0.031	0.031	7.500	9.380	---	20.40	83.25*	---	---	109.09*	---	---	1962 62308
	0.03	44.4	15.010	0.031	0.031	7.500	9.560	---	20.40	83.25*	---	---	107.99*	---	---	1962 62308
T3	S 0.04 R.T. T-L	59.5	7.500	0.040	0.040	0.970	---	---	40.10	50.02	---	---	---	---	---	1966 86734
	0.04	59.5	7.500	0.040	0.040	1.300	---	---	36.80	53.58	---	---	---	---	---	1966 86734
	0.04	59.5	7.500	0.040	0.040	4.060	---	---	15.07	46.85	---	---	---	---	---	1966 86734
	0.04	59.5	7.500	0.040	0.040	2.000	---	---	30.10	55.82	---	---	---	---	---	1966 86734
	0.04	59.5	7.500	0.040	0.040	0.750	---	---	44.70	48.82*	---	---	---	---	---	1966 86734
	0.04	59.5	7.500	0.040	0.040	0.500	---	---	46.00	40.88*	---	---	---	---	---	1966 86734
	0.04	59.5	7.500	0.040	0.040	4.200	---	---	12.14	39.06	---	---	---	---	---	1966 86734

*NOTE - NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

ALUMINUM		2024 (ALCLAD)		K(C)		CRACK LENGTH GROSS STRESS												
CONDITION	--PRODUCT-- FORM THICK TEMP OR (IN) (F)	TEST SPEC YIELD STR (KSI)	---SPECIMEN---		WIDTH THICK (IN)		INIT FINAL ONSET (KSI)		MAX (KSI)		K(APP) STAN MEAN DEV (KBI*BERT IN)		K(C) STAN MEAN DEV DATE REFER					
			M	B	2A(D)	2A(F)	S(D)	S(MAX)	48	9/	6.1	---	---	---	---			
T3	S	0.04	R.T.	T-L	7.500	0.040	2.060	---	29.30	35.30	---	---	---	1966	86734			
		0.04			7.500	0.040	0.500	---	45.70	40.61*	---	---	---	1966	86734			
		0.04			7.500	0.040	0.950	---	45.00	41.97*	---	---	---	1966	86734			
		0.04			7.500	0.040	4.000	---	15.76	48.29	---	---	---	1966	86734			
		0.04			7.500	0.040	4.710	---	11.93	42.22	48	9/	6.1	---	1966	86734		
T3	S	0.04	R.T.	T-L	43.3	29.990	0.041	15.000	18.620	---	17.20	99.30	124.20*	1962	62308			
		0.04			43.3	30.020	0.040	15.000	16.200	---	19.10	110.23*	118.44*	1962	62308			
T3	S	0.06	R.T.	T-L	46.2	2.000	0.064	0.623	1.120	32.30	33.50	35.24*	59.69*	1973	86213			
		0.06			46.2	2.000	0.064	0.622	1.100	32.00	33.50	35.24*	54.64*	1973	86213			
T3	S	0.06	R.T.	T-L	43.4	6.000	0.060	2.000	2.200	---	29.30	99.81*	59.48*	1966	86734			
T3	S	0.06	R.T.	T-L	50.7	7.500	0.064	0.500	---	---	41.50	36.88*	---	1966	86734			
		0.06			50.7	7.500	0.064	4.400	---	---	14.63	49.46	---	1966	86734			
		0.06			50.7	7.500	0.064	4.500	---	---	12.14	42.10	---	1966	86734			
		0.06			50.7	7.500	0.064	4.090	---	---	16.13	50.58	---	1966	86734			
		0.06			50.7	7.500	0.064	2.000	---	---	30.50	56.56*	---	1966	86734			
		0.06			50.7	7.500	0.064	4.160	---	---	19.92	50.72	---	1966	86734			
		0.06			50.7	7.500	0.064	0.660	---	---	40.00	40.92*	---	1966	86734			
		0.06			50.7	7.500	0.064	0.500	---	---	42.00	37.32*	---	1966	86734			
		0.06			50.7	7.500	0.064	1.950	---	---	30.30	95.36*	---	1966	86734			
		0.06			50.7	7.500	0.064	1.000	---	---	37.60	47.65*	---	1966	86734			
		0.06			62.6	7.500	0.064	0.500	---	---	42.90	38.12	---	1966	86734			
		0.06			62.6	7.500	0.064	0.750	---	---	42.30	46.20	---	1966	86734			
		0.06			62.6	7.500	0.064	0.500	---	---	44.40	39.46	---	1966	86734			
		0.06			62.6	7.500	0.064	2.300	---	---	27.10	54.72	---	1966	86734			
		0.06			62.6	7.500	0.064	1.000	---	---	40.30	51.07	---	1966	86734			
		0.06			62.6	7.500	0.064	2.170	---	---	30.00	58.43	---	1966	86734			
		0.06			62.6	7.500	0.064	1.110	---	---	37.50	50.20	---	1966	86734			
		0.06			62.6	7.500	0.064	0.750	---	---	41.70	49.54	48	1/	6.0	---	1966	86734
T3	S	0.06	R.T.	T-L	43.4	9.000	0.060	3.000	3.600	---	28.60	66.71*	75.61*	1966	86734			

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

CONDITION	ALUMINUM		2024 (ALCLAD)		K(C)		CRACK LENGTH GROSS STRESS						K(APP) STAN		K(C) STAN	
	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR STR (KSI)	YIELD (KSI)	---SPECIMEN---		INIT		FINAL ONSET		MAX		K(APP) MEAN DEV		K(C) MEAN DEV	
					WIDTH (IN)	THICK B	(IN)	2A(F)	(IN)	S(O)	(KSI)	S(MAX)	(KSI*SQRT IN)	MEAN	DEV	(KSI*SQRT IN)
T3	S	0.06	R T	43.4	15.000	0.060	5.000	5.900	---	23.70	71.37*	---	79.91*	---	1966	86734
		0.06		43.4	15.000	0.060	5.000	5.800	---	24.00	72.28*	---	79.94*	---	1966	86734
T3	S	0.06	R T	46.6	15.810	0.064	4.000	---	---	28.40	74.14*	---	---	---	1973	86213
		0.06		46.6	15.810	0.064	3.000	---	---	32.10	71.27*	---	---	---	1973	86213
		0.06		46.6	15.810	0.065	6.010	7.140	---	21.20	71.63	---	81.51*	---	1973	86213
		0.06		46.6	15.820	0.064	1.010	1.920	---	46.40	98.59*	---	81.32*	---	1973	86213
T3	S	0.06	R T	43.4	18.000	0.060	6.000	7.000	---	22.10	72.91	---	80.97*	---	1966	86734
		0.06		43.4	18.000	0.061	6.000	6.900	---	22.30	73.57	---	80.87*	---	1966	86734
T3	S	0.06	R T	43.4	21.000	0.060	7.000	8.400	---	20.70	73.76	---	83.60	---	1966	86734
		0.06		43.4	21.000	0.060	7.000	8.600	---	21.05	75.01	---	86.49*	---	1966	86734
T3	S	0.06	R T	43.4	24.000	0.061	8.000	9.600	---	21.60	82.28	---	93.25*	---	1966	86734
		0.06		43.4	24.000	0.060	8.000	9.500	---	20.80	79.23	---	89.12	---	1966	86734
T3	S	0.06	R T	44.9	47.000	0.061	24.000	25.050	---	18.10	133.29*	---	138.76*	---	1966	86734
T3	S	0.09	82 T-L	44.3	3.000	0.092	1.230	2.473	---	27.60	42.90*	---	104.10*	---	1973	86213
		0.09		44.3	3.000	0.091	1.220	2.442	---	28.00	43.26*	---	102.18*	---	1973	86213
		0.09		44.3	3.000	0.092	1.220	2.514	---	28.00	43.26*	---	110.90*	---	1973	86213
		0.09		45.2	3.000	0.092	1.200	2.504	---	27.70	42.28*	---	108.41*	---	1973	86213
		0.09		45.2	3.000	0.092	1.200	2.480	---	27.10	41.37*	---	103.14*	---	1973	86213
		0.09		45.2	3.000	0.091	1.300	2.653	---	26.30	42.63*	---	126.10*	---	1973	86213
		0.09		45.4	3.000	0.092	1.250	2.539	---	26.90	42.32*	---	109.74*	---	1973	86213
		0.09		45.4	3.000	0.092	1.230	2.525	---	27.10	42.12*	---	108.65*	---	1973	86213
		0.09		45.4	3.000	0.092	1.220	2.381	---	27.80	42.95*	---	95.18*	---	1973	86213

BUCKLING OF CRACK EDGES NOT RESTRAINED

T86	S	0.06	R T	65.8	2.000	0.063	0.625	1.030	---	34.70	36.57	---	53.13*	---	1973	86213
		0.06		65.8	2.000	0.063	0.625	0.940	---	32.90	34.68	---	46.48*	---	1973	86213

*NOTE - NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.2.1 (Con't)

CONDITION	ALUMINUM		2024 (ALCLAD)		K(C)		CRACK LENGTH GROSS STRESS						K(C) STAN		K(C) STAN	
	PRODUCT-- FORM THICK TEMP OR (IN) (F)	TEST SPEC YIELD STR (KSI)	WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	STAN DEV	K(C) (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
T86	S	0.06 R.T. T-L 0.06	2.000	0.063	0.625	0.970	---	30.90	32.57	---	44.84*	---	44.84*	---	1973	86213
			2.000	0.063	0.625	0.860	---	30.30	31.94	---	39.86*	---	39.86*	---	1973	86213

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.6.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.6.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2024
CONDITION: T3
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.33		
A:	8.49	1.44			
B:	5.87		1.12		
C:					
D:					
	6.00		1.23		
	7.00		2.32		
	8.00		3.67		
	9.00	2.02	5.25		
	10.00	3.32	7.07		
	13.00	7.71	14.4		
	16.00	12.3	27.0		
	20.00	21.6	62.6		
	25.00	51.1	192.		
	30.00	154.			
A:	30.54	176.			
B:	28.15		403.		
C:					
D:					

ROOT MEAN SQUARE 11.73 9.35
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2 4
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T3
 FORM: 0.09" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 13.30 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 45.8 KSI
 ULT. STRENGTH: 66.6 KSI
 SPECIMEN THK: 0.090"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 86213

ALUM.
ALLOY

2024
(ALCLAD)

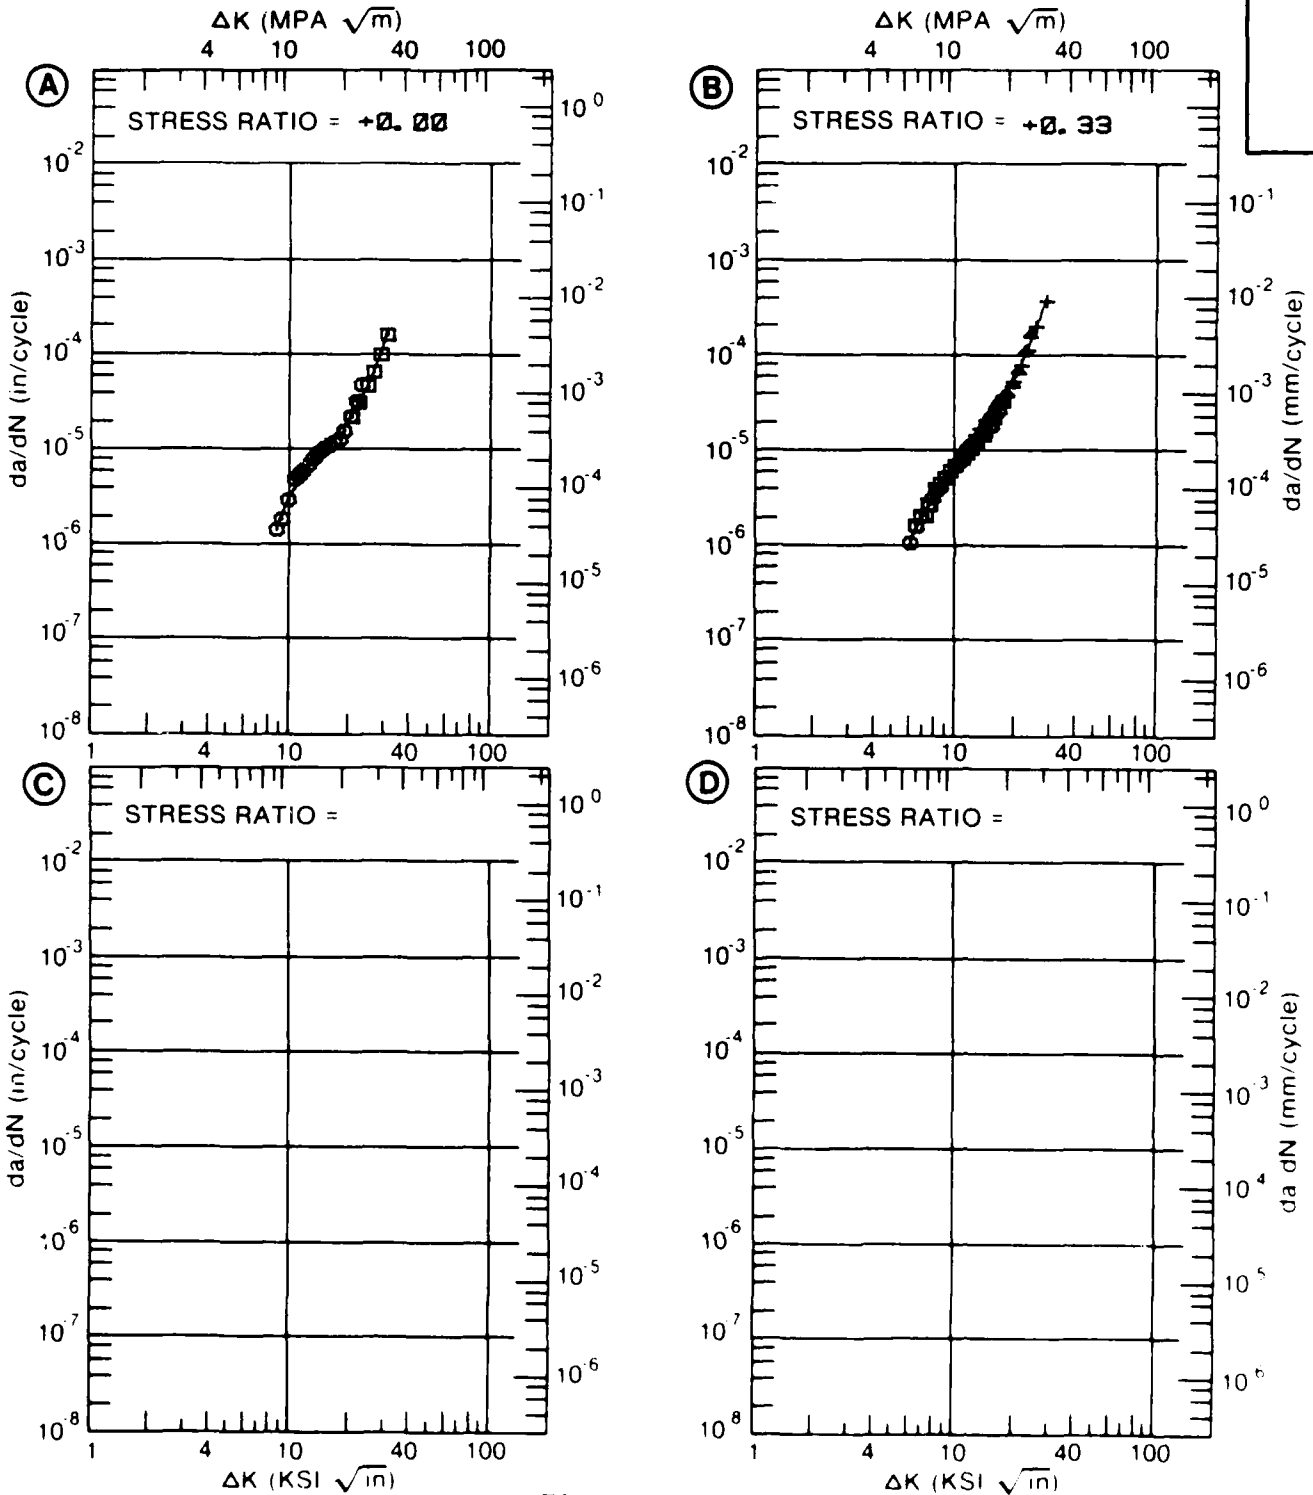


Figure 7.6.3.1

TABLE 7.7.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 2048 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{1C} ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
		PLATE
		L-I
		I-L
		S-L
T651	37.9 ± 1.9 (22)	30.6 ± 2.5 (24)
		25.4 ± 1.9 (18)

TABLE 7.7.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2048

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT DRY AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2	5	10	20	50	100
T851	PLATE	0.33	2 00-20.00		4.99	56.3				
T851	PLATE	0.33	2 00-20.00		3.24					

TABLE 7.7.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2048

TEST CONDITIONS

SPECIMEN

ORIENTATION L-T

ENVIRONMENT S.T.H.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
T851	PLATE	0.33	2.00-20.00								9.14
T851	PLATE	0.33	2.00-20.00								9.60

TABLE 7.7.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2048

TEST CONDITIONS

SPECIMEN ORIENTATION 1-1

ENVIRONMENT DRY AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 10 20 50 100	
1051	PLATE	0.33	2.00-20.00		0.58
1051	PLATE	0.33	2.00-30.00		0.84

TABLE 7.7.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2048

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: S T W AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
T851	PLATE	0.33	2.00-30.00	0.08	0.82 11.9
T851	PLATE	0.33	2.00-20.00	1.01	10.4
T851	PLATE	0.67	2.00-30.00	1.52	24.6

TABLE 7.7.2.1

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	SPECKLE		WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)				M	B									
T851	P	4.00	59.1	R.T.	L-T	4.000	2.000	CT	2.000	2.000	1.07	38.60			1977	AL001
		4.00	59.1			4.000	2.000	CT	2.040	2.040	1.06	38.40			1977	AL001
		1.00	62.1			2.000	1.000	CT	1.030	1.030	0.97	38.70			1977	AL001
		2.00	63.7			4.000	1.980	CT	2.060	2.060	1.11	42.40			1977	AL001
		2.00	63.7			4.000	1.980	CT	2.070	2.070	0.97	39.60			1977	AL001
		3.00	64.2			6.000	3.000	CT	3.120	3.120	0.80	36.40			1977	AL001
		4.00	64.2			4.000	2.000	CT	2.010	2.010	0.79	35.20			1977	AL001
		3.00	64.2			6.000	3.000	CT	3.140	3.140	0.84	37.20			1977	AL001
		4.00	64.2			4.000	2.000	CT	2.020	2.020	0.77	36.20			1977	AL001
		3.00	64.2			6.000	3.000	CT	3.120	3.120	0.83	37.00			1977	AL001
		4.00	64.2			4.000	2.000	CT	2.020	2.020	0.80	36.40			1977	AL001
		3.00	64.7			6.000	3.000	CT	3.060	3.060	0.89	38.50			1977	AL001
		3.00	64.7			6.000	3.000	CT	3.080	3.080	0.84	37.60			1977	AL001
		3.00	64.7			6.000	3.000	CT	3.070	3.070	0.90	38.80			1977	AL001
		2.00	65.4			4.000	1.980	CT	2.060	2.060	0.88	38.40			1977	AL001
		2.00	65.4			4.000	1.980	CT	2.040	2.040	0.90	39.30			1977	AL001
		1.00	67.5			2.000	1.000	CT	1.040	1.040	0.70	35.70			1977	AL001
		1.00	67.5			2.000	1.000	CT	1.040	1.040	0.70	35.70			1977	AL001
	1.00	67.5			2.000	1.000	CT	1.020	1.020	0.68	35.20	37.9/	1.9	1977	AL001	
T851	P	4.00	57.3	R.T.	T-L	4.000	2.000	CT	2.020	2.020	0.61	28.40			1977	AL001
		4.00	57.3			4.000	2.000	CT	2.060	2.060	0.61	28.30			1977	AL001
		1.00	61.1			2.000	1.000	CT	1.030	1.030	0.60	28.00			1977	AL001
		1.00	61.1			2.000	1.000	CT	1.030	1.030	0.67	31.70			1977	AL001
		1.00	61.1			2.000	1.000	CT	1.040	1.040	0.67	31.70			1977	AL001
		4.00	61.9			4.000	2.000	CT	2.030	2.030	0.65	31.80			1977	AL001
		4.00	61.9			4.000	2.000	CT	2.060	2.060	0.45	26.60			1977	AL001
		4.00	61.9			4.000	2.000	CT	2.040	2.040	0.46	26.60			1977	AL001
		2.00	62.6			4.000	1.980	CT	2.050	2.050	0.57	30.00			1977	AL001
		2.00	62.6			4.000	1.980	CT	2.060	2.060	0.59	29.40			1977	AL001
		3.00	62.9			6.000	3.000	CT	3.100	3.100	0.56	29.70			1977	AL001
		3.00	62.9			6.000	3.000	CT	3.140	3.140	0.70	33.30			1977	AL001
		3.00	62.9			6.000	3.000	CT	3.140	3.140	0.73	33.90			1977	AL001
		3.00	62.9			6.000	3.000	CT	3.070	3.070	0.71	33.60			1977	AL001
		3.00	63.9			6.000	3.000	CT	3.240	3.240	0.70	33.70			1977	AL001

TABLE 7.7.2.1 (Con't)

CONDITION	ALUMINUM		2048		K(1C)		YIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	DESIGN DEBION	CRACK LENGTH (IN)	2.5* (K(1C)/TVB)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER
	FORM	THICK (IN)	WIDTH (IN)	W	A	B									
T851	P	3.00	R. T.	T-L	63.9	3.000	CT	3.280	0.72	34.30		30.6/	2.9	1977	AL001
					63.9	3.000	CT	3.240	0.73	34.90		1977	AL001		
					64.9	4.000	CT	2.090	0.52	29.90		1977	AL001		
					64.9	4.000	CT	2.070	0.55	30.40		1977	AL001		
					64.9	4.000	CT	2.050	0.53	29.90		1977	AL001		
					65.4	2.000	CT	1.060	0.56	30.70		1977	AL001		
					65.4	2.000	CT	1.050	0.55	30.70		1977	AL001		
					65.4	2.000	CT	1.050	0.56	31.00		1977	AL001		
					65.4	2.000	CT	1.050	0.56	31.00		1977	AL001		
T851	P	4.00	R. T.	S-L	56.0	3.000	CT	1.530	0.59	26.20				1977	AL001
					56.0	3.000	CT	1.530	0.48	24.60		1977	AL001		
					56.0	3.000	CT	1.530	0.52	25.60		1977	AL001		
					58.5	2.500	CT	1.280	0.38	22.90		1977	AL001		
					58.5	2.500	CT	1.280	0.41	23.70		1977	AL001		
					58.5	2.500	CT	1.280	0.38	22.80		1977	AL001		
					58.9	2.500	CT	1.290	0.65	30.00		1977	AL001		
					58.9	2.500	CT	1.290	0.50	28.80		1977	AL001		
					58.9	2.500	CT	1.290	0.52	26.80		1977	AL001		
					59.3	1.500	CT	0.770	0.43	24.70		1977	AL001		
					59.3	1.500	CT	0.770	0.43	24.70		1977	AL001		
					59.3	1.500	CT	0.780	0.46	25.30		1977	AL001		
					59.5	3.000	CT	1.520	0.42	24.90		1977	AL001		
					59.5	3.000	CT	1.520	0.42	24.30		1977	AL001		
					59.5	3.000	CT	1.520	0.40	23.90		1977	AL001		
59.9	1.500	CT	0.780	0.47	26.00		1977	AL001							
59.9	1.500	CT	0.780	0.48	26.20		1977	AL001							
59.9	1.500	CT	0.780	0.48	26.20		1977	AL001							
59.9	1.500	CT	0.780	0.48	26.20		1977	AL001							

TABLE 7.7.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.7.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2048			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. : DRY AIR	E= R. T. S. T. W.		
DELTA K	A: 5.67	.484			
MIN	B: 5.12		.924		
	C:				
	D:				
	6.00	.567	2.07		
	7.00	.909	3.56		
	8.00	1.43	5.32		
	9.00	2.19	7.58		
	10.00	3.24	9.60		
	13.00	8.78	14.5		
	16.00	19.0			
DELTA K	A: 19.95	40.4			
MAX	B: 14.65		23.7		
	C:				
	D:				
ROOT MEAN SQUARE		20.95	12.60		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 20.00 HZ

YIELD STRENGTH: 67.5 KSI
 ULT. STRENGTH: 71.4 KSI
 SPECIMEN THK: 1.00 "
 SPECIMEN WIDTH: 3.905"
 REFERENCES: AL001

ALUM.
ALLOY

2048

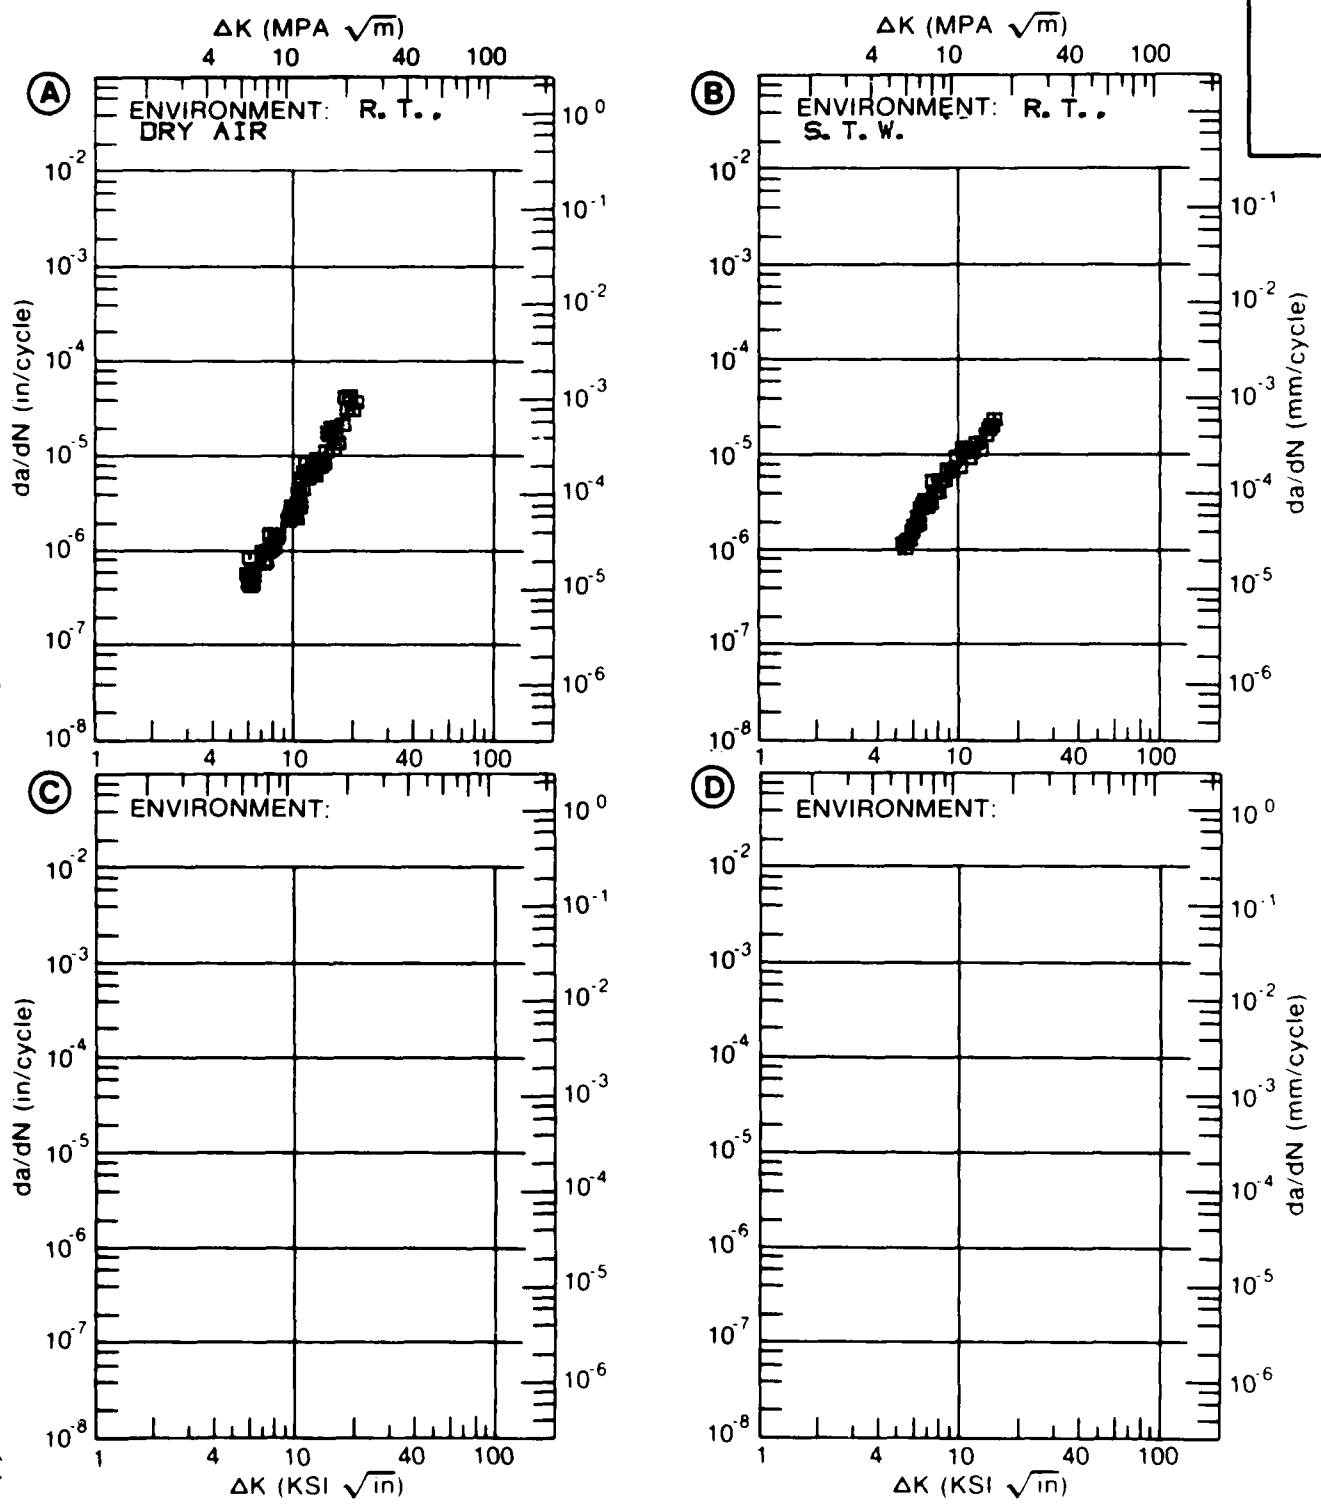


Figure 7.7.3.1

TABLE 7.7.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.7.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2048			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. S. T. W.	
DELTA K	A: 5.67	.855			
MIN	B: 5.67		1.36		
	C: 4.50			.843	
	D:				
	5.00			1.01	
	6.00	.895	1.73	2.04	
	7.00	1.25	3.09	3.93	
	8.00	2.01	4.77	6.02	
	9.00	3.37	6.76	8.13	
	10.00	5.58	9.12	10.4	
	13.00	19.2	19.7	20.2	
	16.00	40.5	40.6		
DELTA K	A: 19.81	152.			
MAX	B: 18.55		76.1		
	C: 15.99			45.9	
	D:				
ROOT MEAN SQUARE		22.75	13.68	13.37	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 20.00 HZ

YIELD STRENGTH: 85.4 KSI
 ULT. STRENGTH: 70.5 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL001

ALUM.
 ALLOY

2048

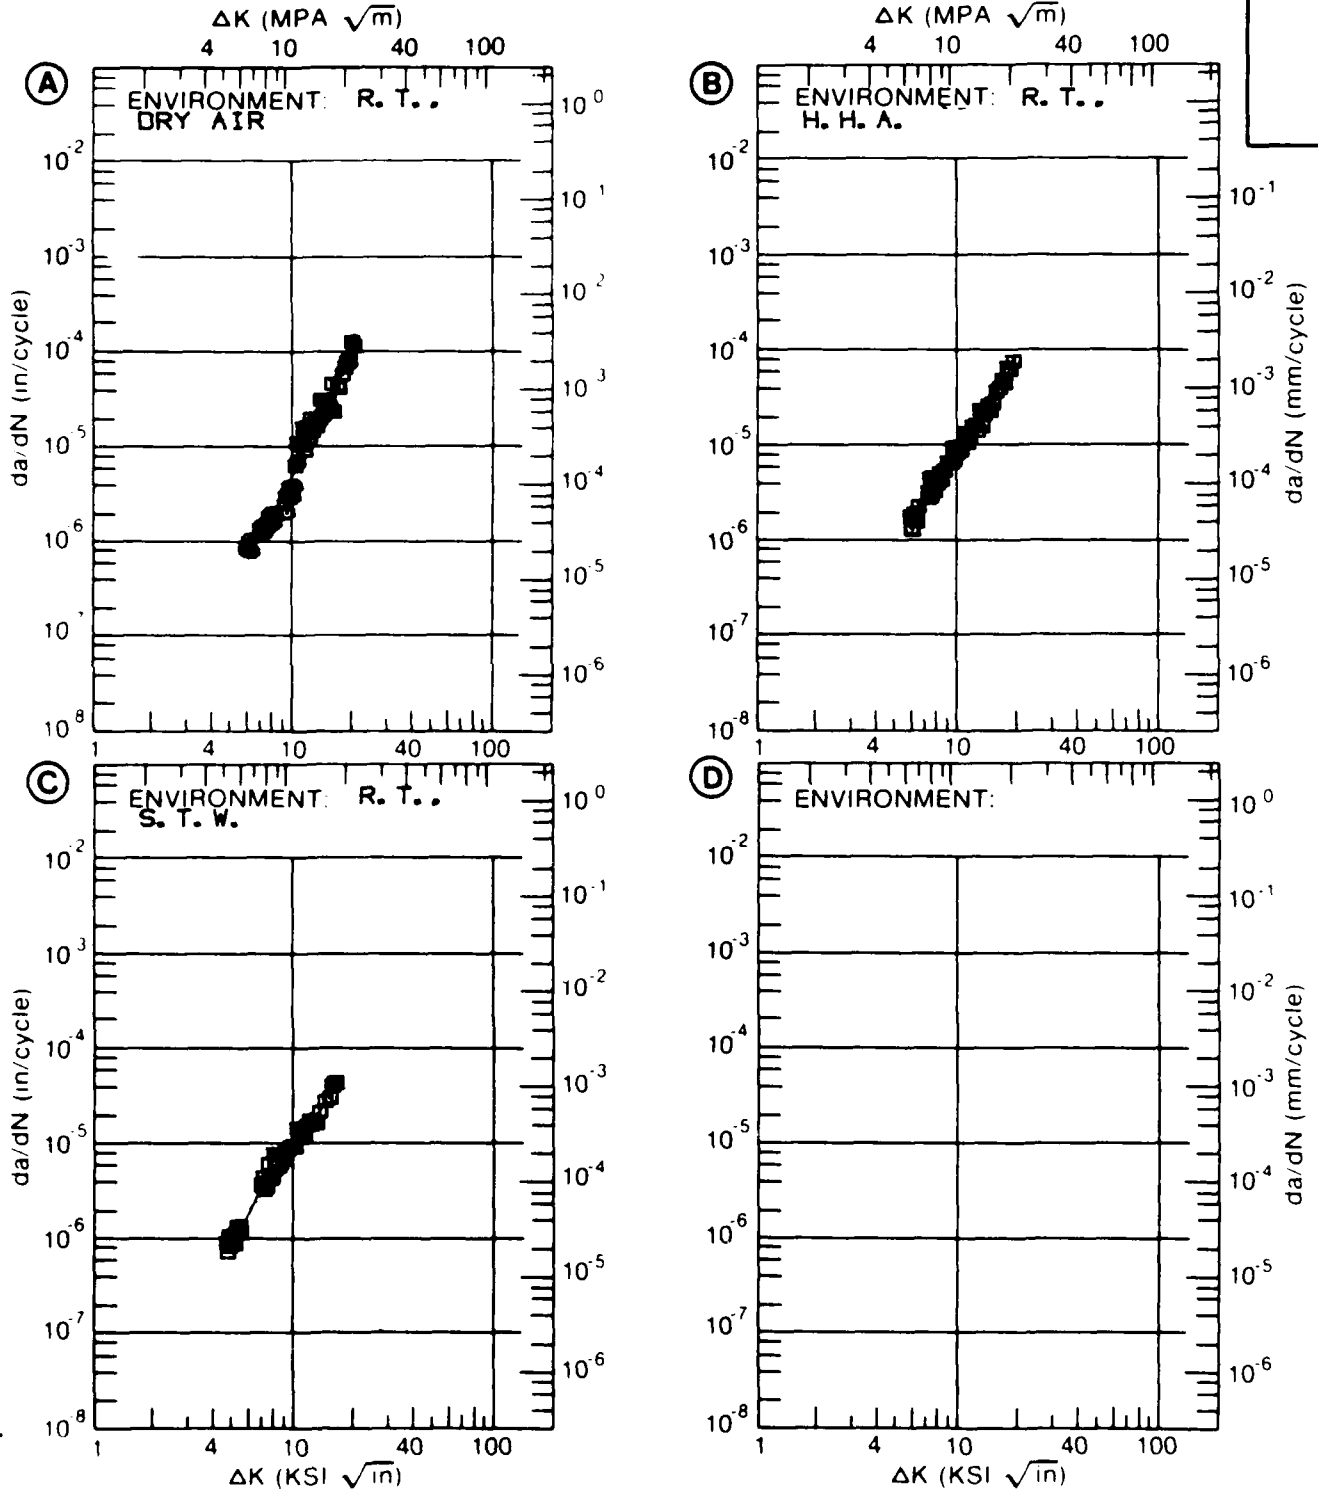


Figure 7.7.3.2

TABLE 7.7.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.7.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2048			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. S. T. W.		
DELTA K	A: 6.42	1.42			
MIN	B: 5.10		.702		
	C:				
	D:				
	6.00		1.67		
	7.00	1.36	3.21		
	8.00	2.51	5.06		
	9.00	3.89	7.06		
	10.00	4.99	9.14		
	13.00	8.78	15.9		
	16.00	19.9			
	20.00	56.3			
DELTA K	A: 20.35	66.6			
MAX	B: 14.76		20.5		
	C:				
	D:				
ROOT MEAN SQUARE		18.85	17.65		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 20.00 HZ

YIELD STRENGTH: 59.1 KSI
 ULT. STRENGTH: 64.4 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.100"
 REFERENCES: AL001

ALUM.
ALLOY

2048

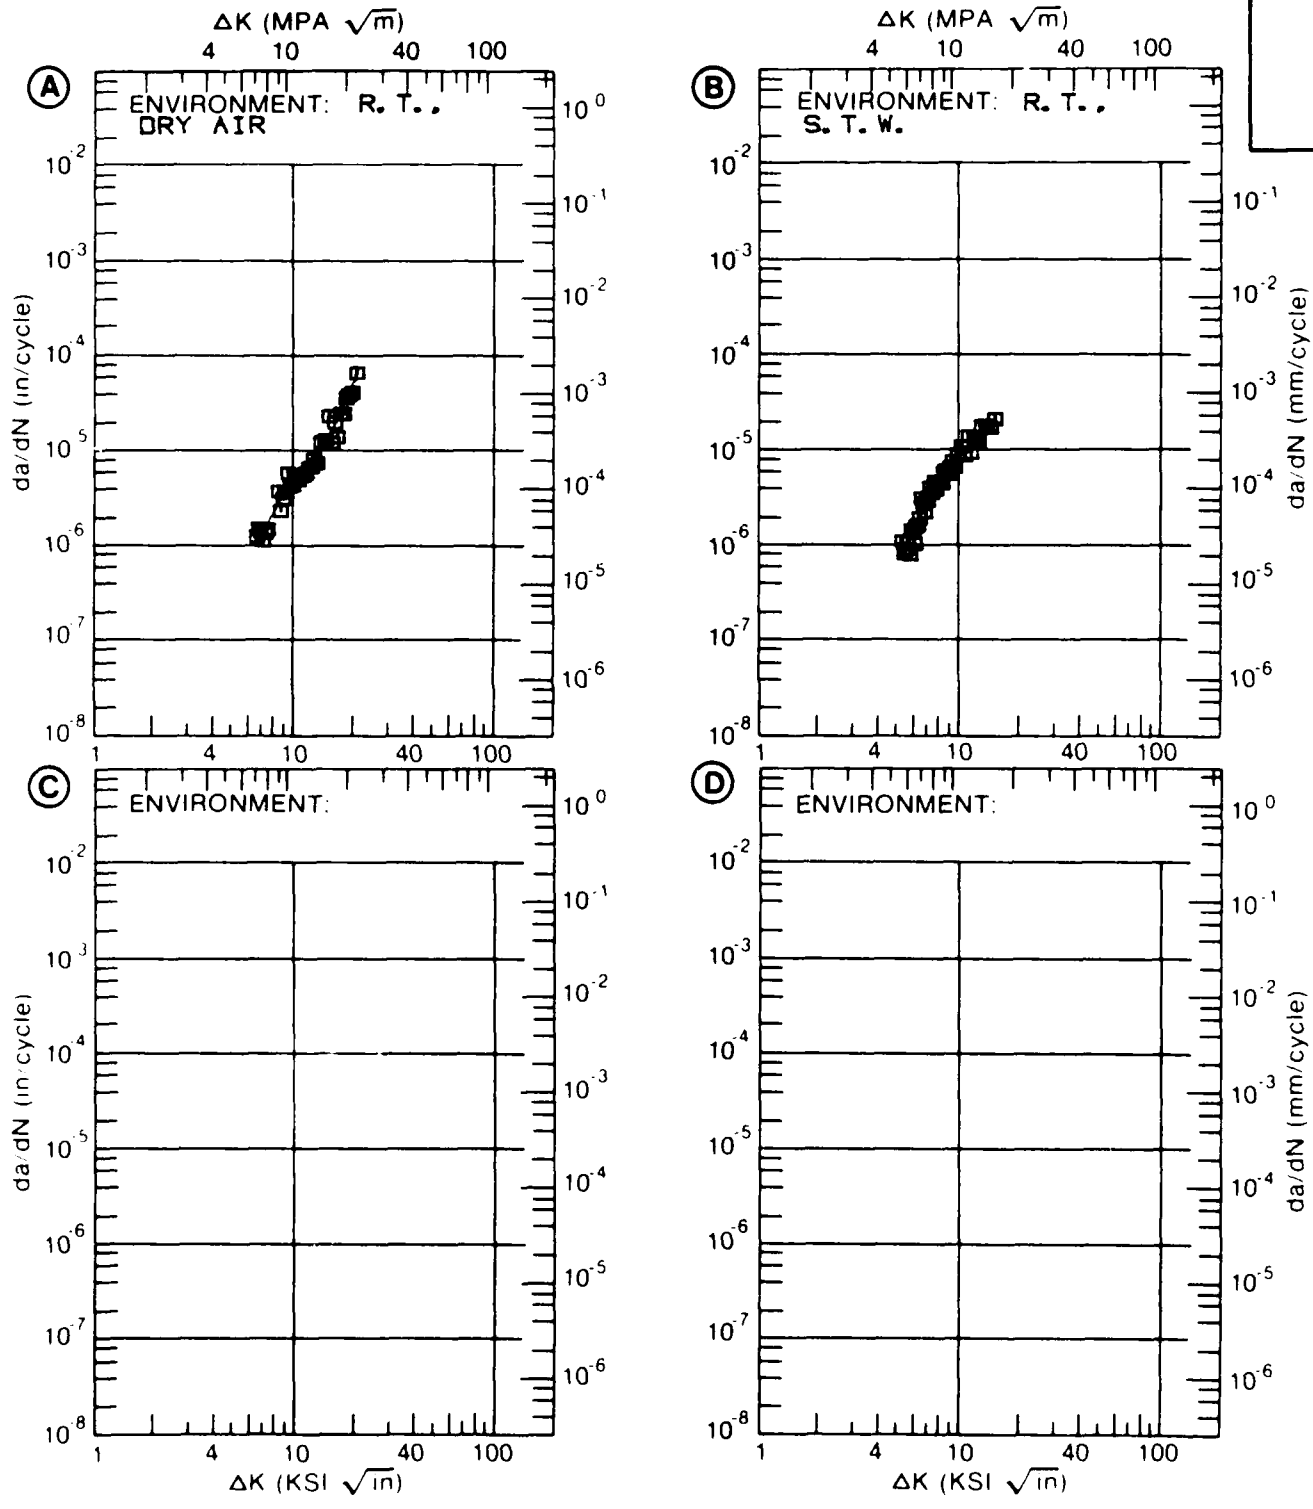


Figure 7.7.3.3

TABLE 7.7.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.7.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2048			
CONDITION: TB51					
ENVIRONMENT: R. T., S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.33	R=+0.67		
DELTA K	A: 2.46	.0795			
MIN	B: 4.19		1.16		
	C:				
	D:				
	2.50	.0819			
	3.00	.128			
	3.50	.212			
	4.00	.344			
	5.00	.825	1.52		
	6.00	1.72	2.61		
	7.00	3.17	4.81		
	8.00	5.30	8.72		
	9.00	8.22	15.1		
	10.00	11.9	24.6		
	13.00	27.7	73.6		
	16.00	55.8			
DELTA K	A: 16.89	118.			
MAX	B: 13.10		75.7		
	C:				
	D:				
ROOT MEAN SQUARE		21.89	16.75		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 2.00- 30.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 57.3 KSI
 ULT. STRENGTH: 83.7 KSI
 SPECIMEN THK: 0.250- 1.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: AL001

ALUM.
 ALLOY
 2048

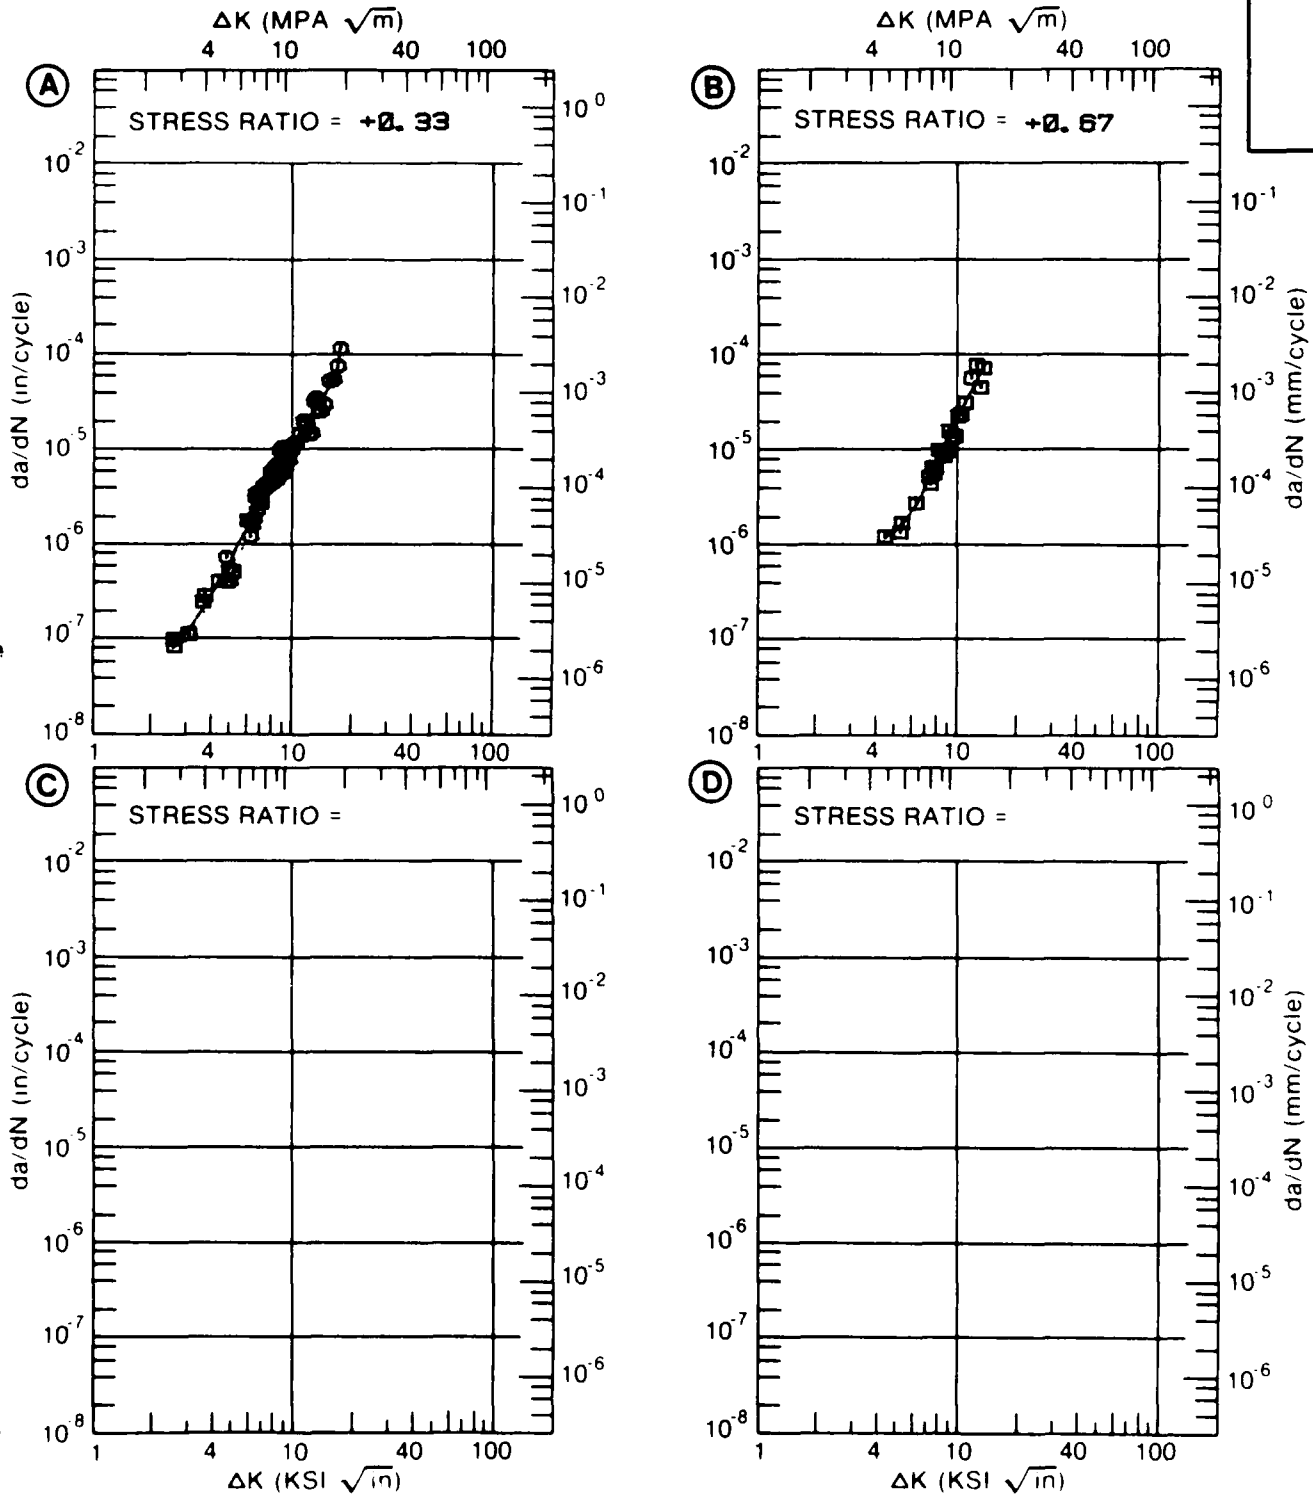


Figure 7.7.3.4

TABLE 7.7.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.7.3.5 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: ALUMINUM		2048			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. S. T. W.		
DELTA K MIN	A: 5.34	.416			
	B: 2.46		.0786		
	C:				
	D:				
	2.50		.0816		
	3.00		.129		
	3.50		.208		
	4.00		.340		
	5.00		.841		
	6.00	.615	1.76		
	7.00	1.16	3.18		
	8.00	2.12	5.20		
	9.00	3.65	7.94		
	10.00	5.84	11.5		
	13.00	15.3	28.6		
	16.00	41.9	58.7		
DELTA K MAX	A: 18.10	148.			
	B: 16.89		70.9		
	C:				
	D:				
ROOT MEAN SQUARE		26.02	23.71		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25				
	1.25-2.0				
	>2.0				

CONDITION/HT: T851
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 30.00 HZ

YIELD STRENGTH: 57.3 KSI
 ULT. STRENGTH: 83.7 KSI
 SPECIMEN THK: 0.250- 1.000"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: AL001

ALUM. ALLOY
2048

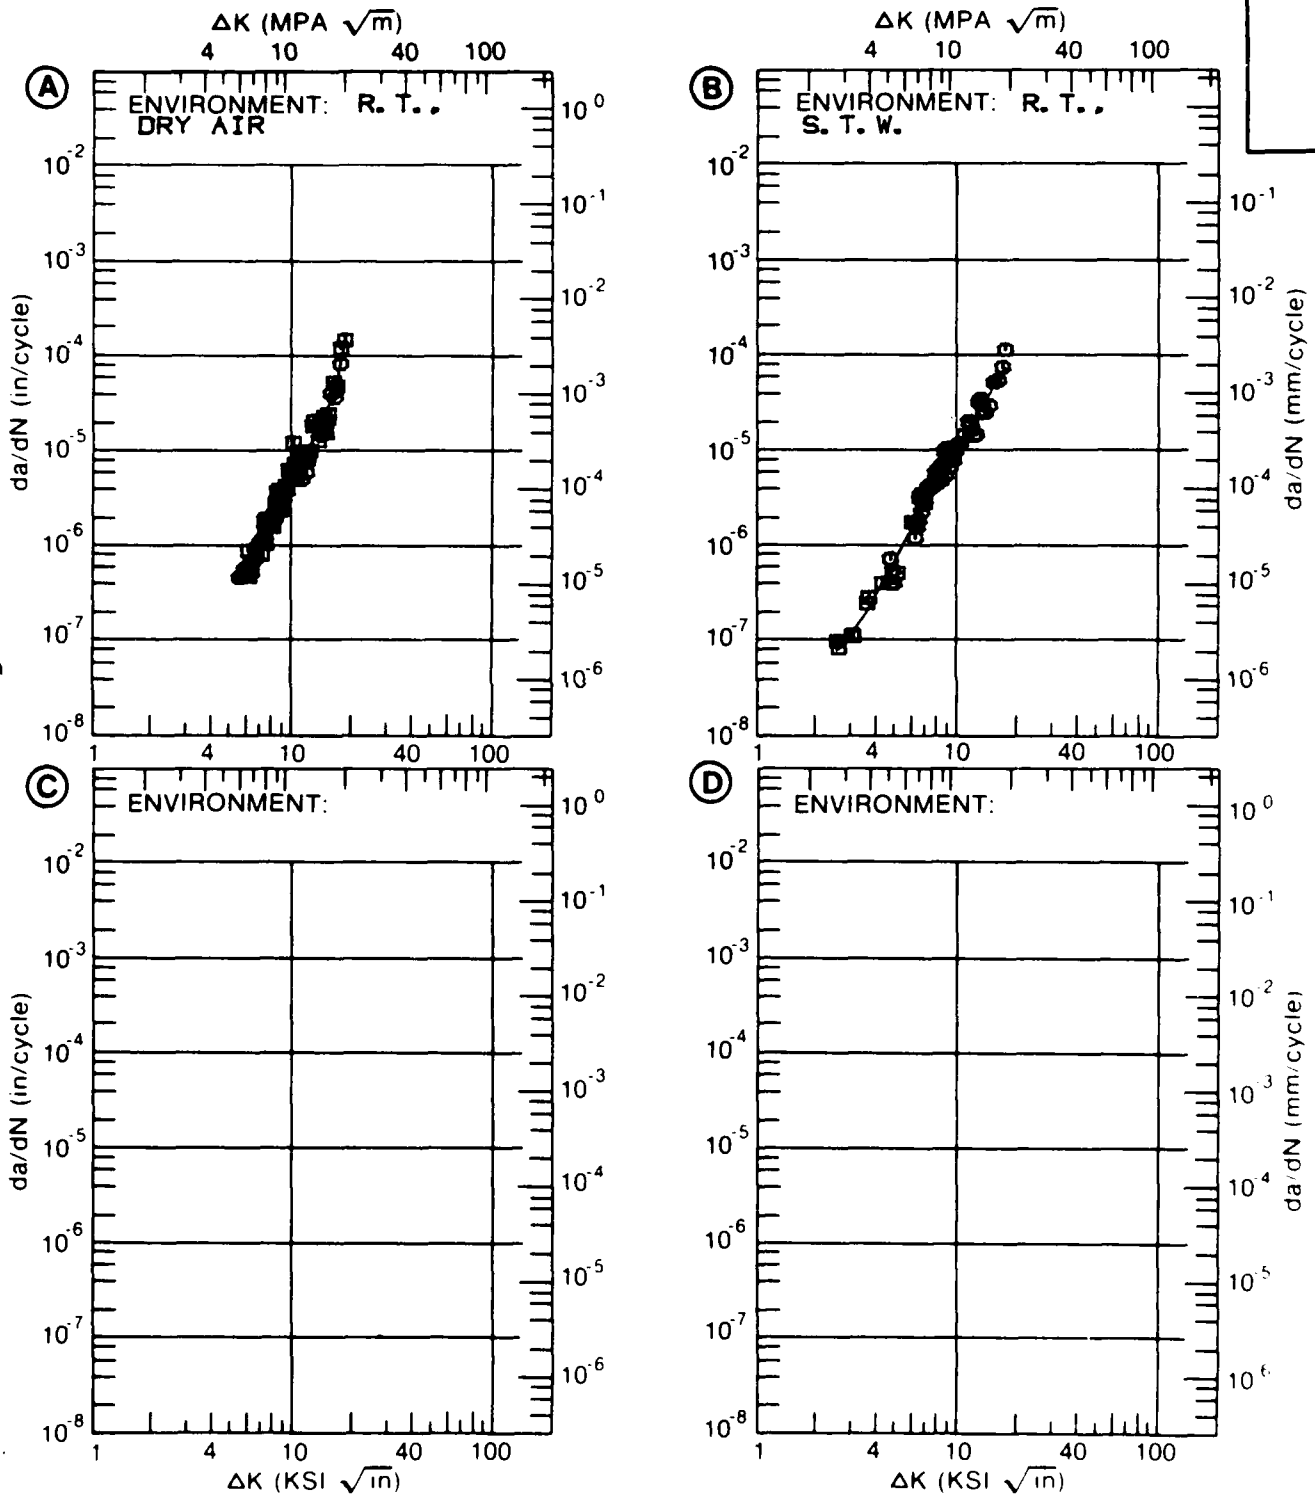


Figure 7.7.3.5

TABLE 7.7.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.7.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2048			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.	E= R. T. S. T. W.		
DELTA K MIN	A: 5.60	1.18			
	B: 4.50		1.08		
	C:				
	D:				
	5.00		1.48		
	6.00	1.70	2.51		
	7.00	3.33	3.97		
	8.00	5.39	6.06		
	9.00	7.99	9.06		
	10.00	11.5	13.4		
	13.00	35.7	41.5		
DELTA K MAX	A: 14.81	78.8			
	B: 15.41		101.		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		17	15.46		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0				

CONDITION/HT: T851
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 20.00 HZ

YIELD STRENGTH: 56.0 KSI
 ULT. STRENGTH: 62.5 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL001

ALUM.
ALLOY

2048

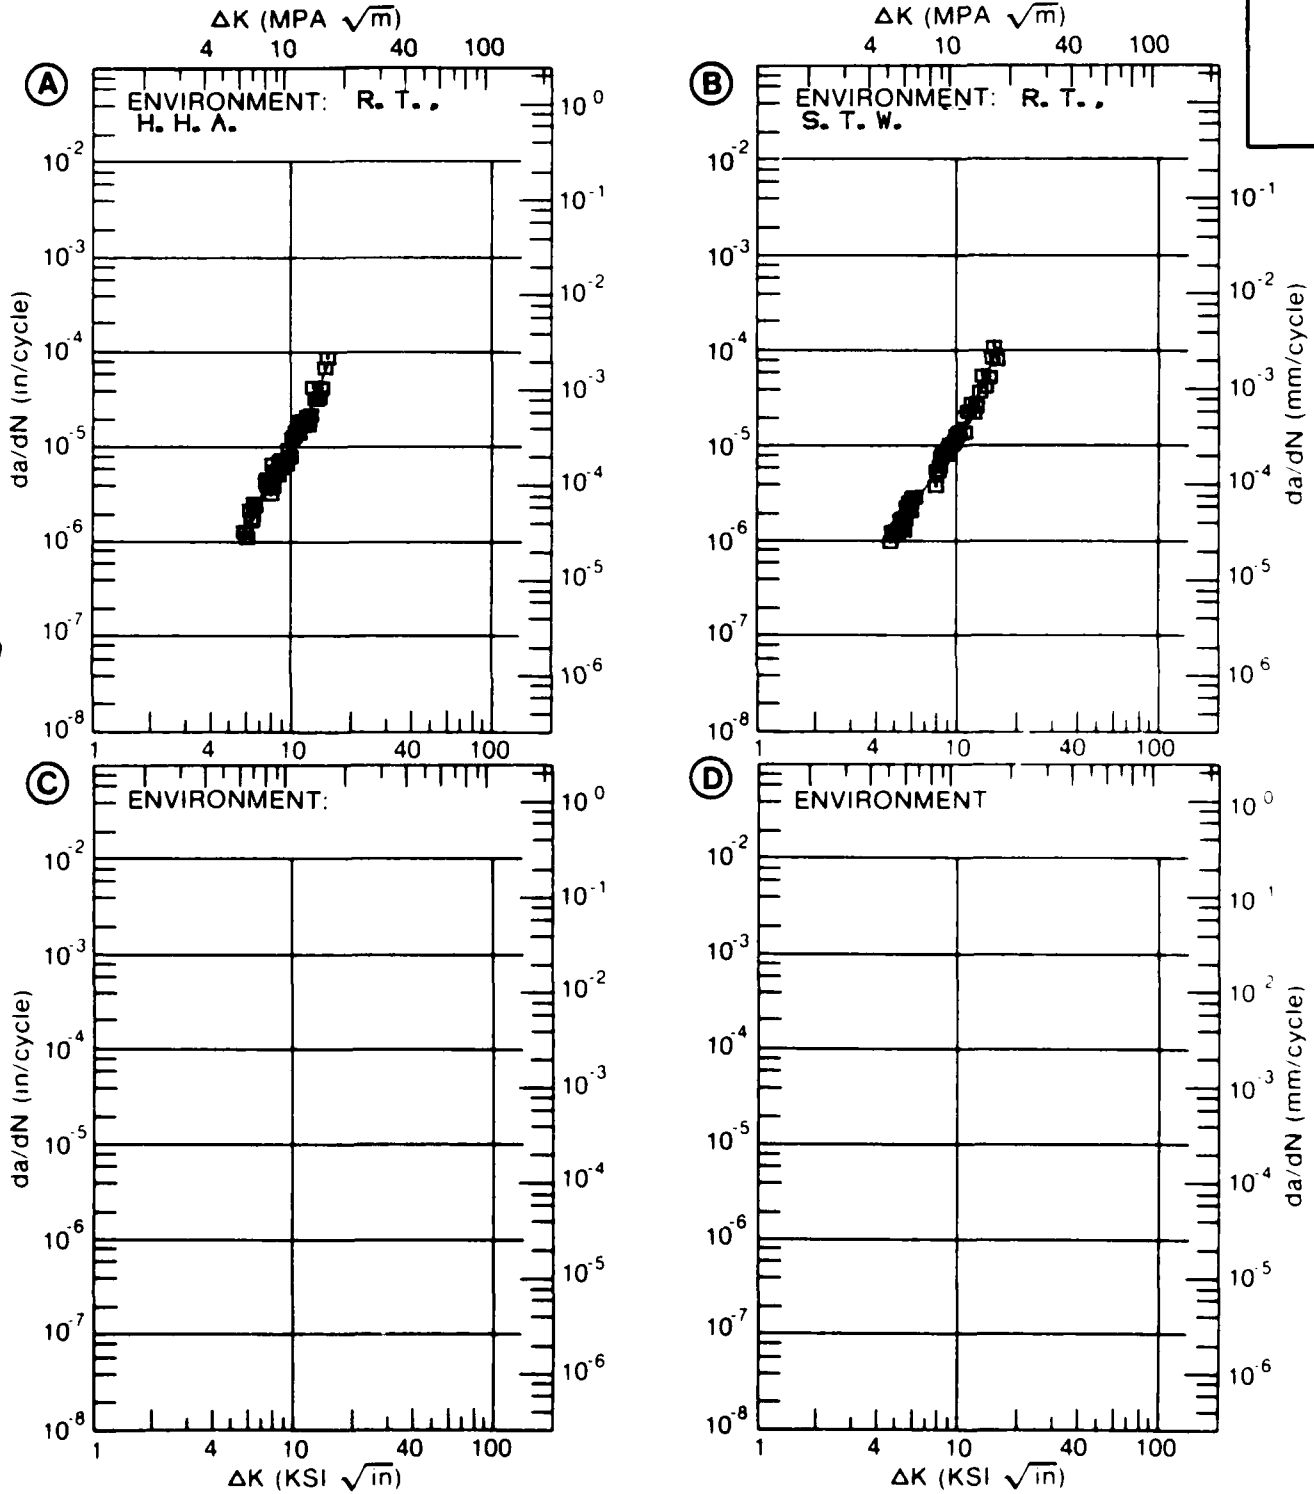


Figure 7.7.3.6

TABLE 7.8.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 2124 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SORT(IN)) DEVIATION			(NUMBER OF SPECIMENS)		
	L-I	I-I	S-I	L-I	I-I	S-I
T851	29 7 ± 2 8 (364)	25 1 ± 2 3 (362)	21 7 ± 2 1 (393)			
T851 (SP)	27 2 ± 4 7 (10)	23 1 ± 2 7 (7)	21 4 ± 3 2 (10)			
T851 (417)	20 9 ± 2 8 (27)	23 8 ± 2 4 (28)	21 3 ± 2 0 (19)			

TABLE 7.8.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2124

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT L-H-A
A-T-R-T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI ^{1/2} SQRT(IN))	2.5	5	10	20	50	100
T851	PLATE	0.10	30.00		0.01	0.26	2.69	44.6		
T851	PLATE	0.50	30.00		0.09	0.68	7.07			

TABLE 7.8.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2124

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: S.T.W
AT R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	2.5	5	10	20	50	100
T851	PLATE	0.10	1.00			0.26	6.04	50.4		
T851	PLATE	0.30	1.00			0.64	8.37	119		
T851	PLATE	0.50	1.00			1.07	9.52			

TABLE 7.8.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2124

TEST CONDITIONS

SPECIMEN ORIENTATION T L

ENVIRONMENT H H A
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)
T851	PLATE	0 10	1 00			0 23	5 53	92 9			
T851	PLATE	0 10	6 00-33 00			0 28	5 16				
T851	PLATE	0 25	6 00-33 00		0 03	0 75	6 15				
T851	PLATE	0 50	1 00			1 22	15 4				
T851	PLATE	0 50	6 00-33 00		0 13	1 17	28 8				

TABLE 7.8.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2124

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT S T W AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5	5 10 20 50 100
T851	PLATE	0.10	1.00		0.37 7.71
T851	PLATE	0.30	1.00		0.59 10.0
T851	PLATE	0.50	1.00		1.08 18.5

TABLE 7.8.1.6
 FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2124

TEST CONDITIONS

SPECIMEN ORIENTATION G-L

ENVIRONMENT S T W
 A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2 5	5	10	20	50	100
TB51	PLATE	0.10	1.00				0.44	7.59	156	
TB51	PLATE	0.30	1.00				0.94	12.4		
TB51	PLATE	0.50	1.00				1.35	19.4		

TABLE 7.8.2.1

CONDITION	ALUMINUM		K(1C)		YIELD STRENGTH (KSI)	THICKNESS (IN)	TEST TEMP (F)	SPECIMEN ORIENT	DESIGNATION	CRACK LENGTH (IN)	2.5* K(1C)/TVS)**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICKNESS (IN)	THICKNESS (IN)	THICKNESS (IN)											
T351 (417)	P	2.50	82	T-L	44.2	3.990	1.999	CT	2.146	1.82	37.70			1973	86213
T851	P	2.55	R.T.	L-T	52.8	6.047	2.504	CT	3.084	1.26	37.90			1978	MPC01
		5.00			55.0	3.000	1.501	CT	1.545	0.95	34.00			1979	GD011
		5.00			55.0	3.003	1.502	CT	1.632	0.93	33.70			1979	GD011
		6.00			55.1	2.974	1.499	CT	1.497	1.02	35.30			1978	MPC01
		5.00			55.2	3.011	1.500	CT	1.596	0.60	27.20			1978	MPC01
		6.00			55.5	3.006	1.498	CT	1.503	0.70	29.90			1978	MPC01
		5.50			56.3	3.010	1.498	CT	1.505	1.08	37.20			1978	MPC01
		6.00			56.5	3.014	1.499	CT	1.767	0.81	32.50			1978	MPC01
		5.50			56.7	2.999	1.500	CT	1.513	0.64	28.90			1980	RA001
		5.50			56.8	3.020	1.493	CT	1.480	0.67	29.70			1978	MPC01
		6.00			56.8	1.978	0.998	CT	1.048	0.57	27.20			1978	RA001
		5.00			56.9	1.986	0.997	CT	1.013	0.65	29.50			1978	MPC01
		5.12			56.9	3.000	1.498	CT	1.500	0.90	34.30			1978	MPC01
		6.00			57.1	3.000	1.500	CT	1.550	0.67	29.70			1972	84368
		6.00			57.1	3.000	1.500	CT	1.520	0.65	29.10			1972	84368
		5.25			57.2	3.004	1.498	CT	1.502	0.65	29.30			1978	MPC01
		5.00			57.2	3.029	1.496	CT	1.484	0.84	33.60			1978	MPC01
		4.90			57.3	3.000	1.498	CT	1.530	0.77	32.00			1978	RA002
		5.50			57.4	3.010	1.499	CT	1.565	0.78	32.30			1978	MPC01
		4.50			57.4	3.001	1.499	CT	1.522	0.95	39.40			1980	RA001
		5.00			57.6	3.000	1.499	CT	1.537	0.62	28.90			1979	RA001
		5.25			57.7	2.973	1.502	CT	1.516	0.75	32.30			1978	MPC01
		5.00			57.7	2.999	1.500	CT	1.499	0.63	29.10			1980	RA001
		5.50			57.8	3.022	1.497	CT	1.481	0.65	29.50			1978	MPC01
		5.00			57.8	2.997	1.497	CT	1.521	0.66	29.90			1979	RA001
		4.62			57.9	2.998	1.500	CT	1.499	0.93	35.50			1978	MPC01
		5.50			58.0	3.010	1.497	CT	1.445	0.60	28.80			1978	MPC01
		5.50			58.1	2.971	1.498	CT	1.456	0.57	28.00			1978	MPC01
		5.25			58.1	3.026	1.500	CT	1.513	0.90	35.20			1978	MPC01
		5.00			58.1	3.000	1.498	CT	1.573	0.74	31.79			1978	RA001
		4.90			58.1	2.984	1.500	CT	1.522	0.84	33.90			1978	MPC01
		4.25			58.1	3.005	1.500	CT	1.498	0.57	27.90			1978	RA002
		5.00			58.2	2.999	1.499	CT	1.551	0.65	29.70			1980	RA001
		5.00			58.2	3.002	1.500	CT	1.561	0.48	25.90			1978	MPC01
		5.50			58.3	2.988	1.499	CT	1.464	0.57	28.40			1978	MPC01

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT-- FORM		TEST THICK (IN)	TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		DESIGN	CRACK LENGTH (IN)	2.5* K(KIC)/TYS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	P	W					THICK	B							
1851	P	5 00	R	T	L-T	58 4	2 980	1 498	CT	1 490	0 67	30 90		1978	MPC01
		3 50				58 7	3 004	1 498	CT	1 502	0 72	31 90		1978	MPC01
		5 00				58 7	1 592	0 998	CT	1 016	0 50	26 80		1978	MPC01
		2 50				58 8	3 000	1 498	CT	1 556	0 60	28 90		1980	RA001
		6 00				58 8	2 000	0 995	CT	0 975	0 97	36 70		1980	RA001
		4 50				58 9	2 982	1 498	CT	1 491	0 75	32 70		1978	MPC01
		6 00				58 9	3 014	1 499	CT	1 537	0 67	30 90		1978	MPC01
		4 50				59 0	3 016	1 499	CT	1 478	0 70	31 60		1978	MPC01
		5 50				59 1	2 984	1 501	CT	1 523	0 57	28 60		1978	MPC01
		4 55				59 1	3 001	1 496	CT	1 517	0 75	32 40		1980	RA001
		5 50				59 1	3 000	1 501	CT	1 530	0 70	31 50		1978	MPC01
		6 00				59 2	2 977	1 495	CT	1 518	0 70	31 80		1978	MPC01
		6 00				59 3	2 986	1 493	CT	1 493	0 55	27 90		1978	MPC01
		4 31				59 3	2 000	1 000	CT	1 000	0 50	26 50		1972	84368
		4 31				59 3	2 000	1 000	CT	0 990	0 52	27 00		1972	84368
		4 00				59 3	3 000	1 499	CT	1 542	0 61	29 50		1978	RA001
		4 90				59 4	2 990	1 368	CT	1 465	0 57	29 00		1978	MPC01
		4 00				59 4	2 000	1 000	CT	1 000	0 61	29 40		1972	84368
		4 00				59 4	2 000	1 000	CT	1 000	0 59	28 90		1972	84368
		4 62				59 5	2 988	1 478	CT	1 464	0 62	30 10		1978	MPC01
		5 25				59 6	3 018	1 501	CT	1 509	0 81	34 50		1978	MPC01
		6 00				59 6	1 998	0 998	CT	1 033	0 73	32 30		1978	RA001
		4 00				59 6	2 999	1 499	CT	1 527	0 62	29 90		1980	RA001
		4 00				59 6	3 002	1 498	CT	1 542	0 88	35 50		1980	RA001
		4 50				59 6	2 997	1 498	CT	1 532	0 79	33 59		1979	RA001
		4 50				59 6	3 012	1 499	CT	1 476	0 70	31 70		1978	MPC01
		1 81				59 7	3 011	1 498	CT	1 626	0 60	29 80		1978	MPC01
		4 50				59 8	3 000	1 500	CT	1 530	0 76	33 10		1972	84368
		4 50				59 8	3 000	1 500	CT	1 510	0 71	31 90		1972	84368
		6 00				59 9	3 004	1 499	CT	1 532	0 70	31 80		1978	MPC01
		4 00				59 9	3 012	1 497	CT	1 566	0 70	32 30		1978	MPC01
		5 00				59 9	3 004	1 499	CT	1 532	0 60	29 80		1978	MPC01
		3 00				59 9	2 994	1 406	CT	1 529	0 66	30 79		1980	RA001
		3 00				59 9	3 001	1 376	CT	1 484	0 60	29 40		1980	RA001
		4 00				60 0	3 000	1 499	CT	1 489	0 62	29 90		1980	RA001
		5 50				60 1	2 996	1 502	CT	1 528	0 97	29 40		1978	MPC01
		5 50				60 1	3 012	1 501	CT	1 504	0 52	27 70		1978	MPC01
		4 50				60 1	3 000	1 495	CT	1 533	0 67	31 60		1978	RA002
		2 50				60 3	3 002	1 102	CT	1 510	0 44	25 50		1980	RA001

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	SPECIMEN		WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(1C)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)				H	B										
T851	P	4 50	60.3	R.T	L-T	1.499	CT	3.000	1.499	CT	1.536	0.57	28.79			1978 RA002	
		5 00	60.4			1.001	CT	2.000	1.001	CT	1.011	0.56	28.79			1978 RA002	
		5 50	60.4			3.016	CT	3.016	1.500	CT	1.508	0.52	28.00			1978 MPC01	
		5 25	60.4			2.994	CT	2.994	1.500	CT	1.497	0.75	33.50			1978 MPC01	
		5 50	60.4			3.002	CT	3.002	1.500	CT	1.531	0.62	30.30			1978 MPC01	
		2 50	60.5			3.004	CT	3.004	1.499	CT	1.523	0.44	25.40			1980 RA001	
		4 50	60.5			2.978	CT	2.978	1.500	CT	1.489	0.65	31.00			1978 MPC01	
		5 50	60.6			3.004	CT	3.004	1.500	CT	1.532	0.52	28.10			1978 MPC01	
		3 54	60.6			2.994	CT	2.994	1.497	CT	1.587	0.62	30.70			1978 MPC01	
		5 50	60.6			3.026	CT	3.026	1.500	CT	1.513	0.60	30.20			1978 MPC01	
		5 50	60.6			2.998	CT	2.998	1.500	CT	1.529	0.48	26.90			1978 MPC01	
		2 75	60.6			3.001	CT	3.001	1.499	CT	1.591	0.48	26.79			1978 RA002	
		3 00	60.6			3.000	CT	3.000	1.400	CT	1.526	0.64	30.90			1980 RA001	
		3 50	60.8			3.008	CT	3.008	1.497	CT	1.534	0.48	27.10			1978 MPC01	
		3 62	60.8			3.006	CT	3.006	1.476	CT	1.473	0.65	31.40			1978 MPC01	
		3 50	60.8			3.004	CT	3.004	1.496	CT	1.492	0.42	25.00			1980 RA001	
		5 50	60.9			2.980	CT	2.980	1.500	CT	1.520	0.48	27.00			1978 MPC01	
		4 31	60.9			3.004	CT	3.004	1.498	CT	1.592	0.52	28.10			1978 MPC01	
		5 00	60.9			3.010	CT	3.010	1.500	CT	1.535	0.55	29.10			1978 MPC01	
		5 50	60.9			3.028	CT	3.028	1.501	CT	1.514	0.70	32.70			1978 MPC01	
		4 00	60.9			2.999	CT	2.999	1.499	CT	1.544	0.56	28.90			1978 RA001	
		6 00	61.0			2.998	CT	2.998	1.500	CT	1.559	0.70	32.50			1978 MPC01	
		3 50	61.0			3.004	CT	3.004	1.499	CT	1.502	0.72	33.00			1978 MPC01	
		3 50	61.0			2.982	CT	2.982	1.499	CT	1.461	0.70	32.50			1978 MPC01	
		5 50	61.1			3.032	CT	3.032	1.500	CT	1.516	0.48	26.90			1978 MPC01	
		4 25	61.1			1.985	CT	1.985	0.998	CT	1.032	0.78	34.60			1978 MPC01	
		5 50	61.1			3.000	CT	3.000	1.500	CT	1.500	0.53	28.10			1972 84368	
		5 50	61.1			3.000	CT	3.000	1.500	CT	1.500	0.59	28.80			1972 84368	
		4 00	61.1			3.000	CT	3.000	1.499	CT	1.571	0.73	33.09			1979 RA001	
		4 00	61.2			3.000	CT	3.000	1.497	CT	1.586	0.92	37.20			1978 RA001	
		4 00	61.2			3.012	CT	3.012	1.496	CT	1.536	0.67	31.90			1978 MPC01	
		2 70	61.3			2.008	CT	2.008	1.000	CT	1.024	0.81	35.50			1978 MPC01	
		4 90	61.3			3.002	CT	3.002	1.499	CT	1.550	0.50	27.50			1978 RA002	
		3 00	61.3			3.002	CT	3.002	1.497	CT	1.522	0.65	31.40			1980 RA001	
		6 00	61.4			2.980	CT	2.980	1.499	CT	1.520	0.70	32.80			1978 MPC01	
		2 50	61.4			3.020	CT	3.020	1.186	CT	1.540	0.55	29.10			1978 MPC01	
		2 50	61.4			2.012	CT	2.012	0.998	CT	1.006	0.44	26.00			1978 MPC01	
		5 50	61.4			3.031	CT	3.031	1.500	CT	1.545	0.52	28.80			1978 MPC01	
		4 90	61.5			2.976	CT	2.976	1.494	CT	1.488	0.48	27.50			1978 MPC01	

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM	2124	K(IIC)	SPECIMEN		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	THICK (IN)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* K(IIC)/TYS)**2 (IN)	K(IIC) MEAN (KSI*SQRT IN)	K(IIC) STAN DEV (KSI*SQRT IN)	DATE	REFER
				A	B													
T851	P	4.00	R.T.	L-T	61.5	3.001	1.496	CT	1.610	0.65	31.50	1979 RA001						
		3.00			61.5	3.002	1.379	CT	1.551	0.82	35.40	1980 RA001						
		5.50			61.6	3.026	1.500	CT	1.513	0.52	28.80	1978 MPC01						
		4.00			61.6	2.883	1.499	CT	1.550	0.55	29.20	1978 MPC01						
		5.50			61.6	3.018	1.501	CT	1.509	0.42	25.70	1978 MPC01						
		5.50			61.6	2.973	1.500	CT	1.516	0.48	27.40	1978 MPC01						
		5.00			61.6	2.979	1.501	CT	1.549	0.57	30.00	1978 MPC01						
		2.00			61.8	2.994	1.500	CT	1.537	0.59	30.20	1980 RA001						
		3.00			61.9	3.000	1.449	CT	1.536	0.63	31.29	1980 RA001						
		5.50			61.9	2.994	1.501	CT	1.527	0.52	29.00	1978 MPC01						
		2.50			61.9	3.001	1.499	CT	1.513	0.48	27.29	1980 RA001						
		4.25			61.9	3.018	1.502	CT	1.539	0.57	29.80	1978 MPC01						
		5.50			61.9	2.998	1.501	CT	1.529	0.55	29.10	1978 MPC01						
		3.00			61.9	2.980	1.245	CT	1.490	0.65	31.70	1978 MPC01						
		5.50			61.9	3.030	1.501	CT	1.515	0.48	27.30	1978 MPC01						
		5.00			61.9	3.020	1.502	CT	1.540	0.57	30.00	1978 MPC01						
		4.00			62.0	3.008	1.498	CT	1.504	0.78	35.30	1978 MPC01						
		5.00			62.0	2.991	1.499	CT	1.585	0.57	30.10	1978 MPC01						
		5.50			62.0	3.016	1.501	CT	1.508	0.40	25.40	1978 MPC01						
		5.50			62.0	3.012	1.500	CT	1.506	0.42	25.70	1978 MPC01						
		3.50			62.0	3.001	1.490	CT	1.572	0.73	33.59	1979 RA001						
		4.00			62.0	3.014	1.493	CT	1.477	0.67	32.70	1978 MPC01						
		5.50			62.1	2.992	1.500	CT	1.526	0.46	27.10	1978 MPC01						
		5.50			62.1	2.978	1.500	CT	1.519	0.55	29.60	1978 MPC01						
		5.25			62.1	2.980	1.500	CT	1.520	0.62	31.30	1978 MPC01						
		5.50			62.1	2.978	1.500	CT	1.519	0.50	28.20	1978 MPC01						
		4.50			62.1	3.014	1.500	CT	1.507	0.60	30.80	1978 MPC01						
		5.50			62.1	3.008	1.500	CT	1.504	0.46	27.20	1978 MPC01						
		5.50			62.1	2.986	1.503	CT	1.523	0.57	30.80	1978 MPC01						
		4.50			62.1	3.006	1.501	CT	1.503	0.60	30.80	1978 MPC01						
		5.50			62.1	2.998	1.500	CT	1.559	0.58	29.30	1978 MPC01						
		3.54			62.2	3.030	1.499	CT	1.515	0.65	32.10	1978 MPC01						
		4.00			62.2	3.004	1.478	CT	1.562	0.52	29.20	1978 MPC01						
		3.00			62.2	2.998	1.300	CT	1.485	0.63	31.29	1978 RA002						
		1.75			62.2	3.000	1.495	CT	1.528	0.53	28.79	1980 RA001						
		4.50			62.3	3.004	1.501	CT	1.502	0.55	29.90	1978 MPC01						
		4.50			62.3	3.004	1.501	CT	1.502	0.67	32.80	1978 MPC01						
		5.50			62.3	2.988	1.500	CT	1.524	0.42	25.80	1978 MPC01						
		5.50			62.4	3.026	1.500	CT	1.513	0.46	27.30	1978 MPC01						

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	THICK (IN)	FORM	SPECIMEN		DESIGN THICK (IN)	CRACK LENGTH (IN)	K(1C)	K(1C) STAN MEAN DEV (KSI*SQRT IN)	DATE	REFER
	WIDTH (IN)	THICK (IN)													
T651	P	3.25	62.4	L-T	R.T.	3.25		1.498	CT	1.435	0.72	34.00	1978	MPC01	
		2.50	62.5			3.000		1.499	CT	1.600	0.60	30.79	1978	RA002	
		6.00	62.5			3.010		1.499	CT	1.565	0.72	34.00	1978	MPC01	
		4.90	62.9			3.000		1.499	CT	1.603	0.50	28.00	1978	RA002	
		5.00	62.6			3.024		1.500	CT	1.542	0.48	28.00	1978	MPC01	
		5.50	62.6			3.000		1.500	CT	2.100	0.56	29.70	1978	GD003	
		5.50	62.6			3.000		1.500	CT	2.100	0.62	31.20	1978	GD003	
		5.50	62.6			2.986		1.500	CT	1.523	0.52	28.80	1978	MPC01	
		5.00	62.6			3.016		1.500	CT	1.508	0.44	26.90	1978	MPC01	
		4.75	62.6			3.000		1.500	CT	1.546	0.66	32.20	1980	RA001	
		5.50	62.6			3.000		1.500	CT	2.100	0.58	30.20	1978	GD003	
		3.12	62.7			3.015		1.377	CT	1.447	0.65	32.00	1978	MPC01	
		3.12	62.7			3.030		1.498	CT	1.515	0.62	31.60	1978	MPC01	
		3.00	62.7			3.002		1.188	CT	1.581	0.51	28.50	1978	RA002	
		3.75	62.8			3.029		1.497	CT	1.575	0.52	28.90	1978	MPC01	
		4.00	62.8			3.001		1.251	CT	1.525	0.47	27.30	1980	RA001	
		5.00	62.9			3.032		1.500	CT	1.525	0.48	28.20	1978	MPC01	
		5.00	62.9			2.972		1.500	CT	1.516	0.46	27.20	1978	MPC01	
		2.50	62.9			2.000		1.000	CT	---	0.67	32.10	1974	88742	
		5.50	62.9			3.024		1.500	CT	1.512	0.48	28.00	1978	MPC01	
		3.12	62.9			3.002		1.498	CT	1.514	0.67	32.59	1980	RA001	
		4.25	62.9			3.039		1.500	CT	1.550	0.48	27.80	1978	MPC01	
		2.50	62.9			2.000		1.000	CT	---	0.74	33.70	1974	88742	
		2.50	62.9			2.000		1.000	CT	---	0.67	32.00	1974	88742	
		3.12	63.0			3.025		1.498	CT	1.482	0.62	32.10	1978	MPC01	
		4.25	63.0			3.010		1.500	CT	1.535	0.52	29.10	1978	MPC01	
		6.00	63.1			3.002		1.499	CT	1.561	0.62	31.70	1978	MPC01	
		2.00	63.1			3.006		1.500	CT	1.503	0.48	27.90	1978	MPC01	
		2.50	63.1			2.970		1.201	CT	1.574	0.50	28.40	1978	MPC01	
		2.00	63.1			3.020		1.499	CT	1.510	0.55	30.20	1978	MPC01	
		4.25	63.2			2.977		1.500	CT	1.518	0.46	27.40	1978	MPC01	
		4.50	63.2			3.016		1.500	CT	1.508	0.55	30.20	1978	MPC01	
		4.50	63.2			2.984		1.500	CT	1.492	0.57	30.50	1978	MPC01	
		5.00	63.2			3.008		1.500	CT	1.534	0.60	31.40	1978	MPC01	
		4.50	63.2			3.012		1.500	CT	1.506	0.60	31.00	1978	MPC01	
		2.00	63.2			3.000		1.497	CT	1.591	0.50	28.50	1978	RA001	
		2.75	63.2			3.002		1.483	CT	1.520	0.50	28.29	1980	RA001	
		4.50	63.4			3.022		1.499	CT	1.511	0.55	30.30	1978	MPC01	
		4.50	63.4			3.000		1.500	CT	1.520	0.44	26.70	1972	84368	

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		W	SPECIMEN		DESIGN	CRACK LENGTH (IN)	K(1C)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
						M	B		THICK (IN)	WIDTH (IN)								
TB51	P	4.50	R.T.	L-T	63.4	3.000	1.500	CT	1.540	0.46	27.20	1972	B4368					
		1.50			63.4	3.000	1.483	CT	1.568	0.59	30.79	1980	RA001					
		4.25			63.5	2.986	1.500	CT	1.523	0.50	29.20	1978	MPC01					
		4.00			63.5	3.014	1.499	CT	1.567	0.60	31.60	1978	MPC01					
		1.75			63.5	3.004	1.500	CT	1.517	0.53	29.29	1978	RA002					
		1.75			63.6	3.001	1.496	CT	1.583	0.52	29.10	1978	RA001					
		3.00			63.6	1.998	0.999	CT	1.019	0.43	26.50	1979	RA001					
		2.75			63.6	2.999	1.496	CT	1.943	0.54	29.60	1980	RA001					
		3.00			63.6	2.986	1.499	CT	1.523	0.55	29.90	1978	MPC01					
		3.12			63.6	2.985	1.499	CT	1.582	0.70	33.80	1978	MPC01					
		2.50			63.7	3.002	1.499	CT	1.561	0.52	29.70	1978	MPC01					
		4.00			63.7	3.019	1.499	CT	1.570	0.42	26.70	1978	MPC01					
		2.50			63.7	3.001	1.495	CT	1.607	0.53	29.40	1978	RA002					
		2.00			63.8	3.016	1.498	CT	1.508	0.46	27.60	1978	MPC01					
		2.50			63.8	3.010	1.498	CT	1.535	0.52	29.40	1978	MPC01					
		3.62			63.8	2.995	1.499	CT	1.529	0.49	28.29	1980	RA001					
		2.50			63.8	3.000	1.499	CT	1.584	0.56	30.20	1978	RA002					
		3.50			63.9	3.000	1.500	CT	1.520	0.61	31.50	1972	B4368					
		2.35			63.9	3.001	1.500	CT	1.581	0.51	29.00	1978	RA002					
		3.00			63.9	3.000	1.397	CT	1.532	0.54	29.90	1980	RA001					
		4.25			63.9	3.014	1.501	CT	1.507	0.62	32.50	1978	MPC01					
		3.50			63.9	3.000	1.500	CT	1.910	0.61	31.60	1972	B4368					
		3.00			64.0	2.996	1.400	CT	1.618	0.50	29.40	1978	MPC01					
		4.25			64.0	3.020	1.500	CT	1.510	0.62	32.30	1978	MPC01					
		3.00			64.0	3.021	1.247	CT	1.450	0.44	27.50	1978	MPC01					
		4.90			64.0	3.000	1.499	CT	1.572	0.56	30.29	1978	RA002					
		5.50			64.0	2.977	1.500	CT	1.518	0.46	27.90	1978	MPC01					
		3.00			64.1	2.999	1.488	CT	1.574	0.69	33.70	1978	RA001					
		2.50			64.1	3.000	1.499	CT	1.623	0.56	30.40	1978	RA002					
		2.35			64.1	1.498	0.751	CT	0.790	0.20	18.29	1980	RA001					
		3.00			64.2	3.024	1.499	CT	1.548	0.57	30.70	1978	MPC01					
		4.25			64.2	2.000	1.500	CT	1.512	0.46	27.90	1978	RA002					
		2.00			64.2	2.000	1.002	CT	1.008	0.43	26.79	1978	RA002					
	3.50			64.2	2.999	1.499	CT	1.550	0.67	33.40	1978	RA001						
	2.25			64.2	2.989	0.999	CT	1.554	0.36	25.00	1978	MPC01						
	3.00			64.2	3.002	1.495	CT	1.533	0.40	25.70	1980	RA001						
	1.57			64.3	3.000	1.500	CT	1.590	0.46	27.40	1972	B4368						
	3.62			64.3	2.978	1.499	CT	1.608	0.46	27.80	1978	MPC01						
	3.54			64.3	3.014	1.498	CT	1.507	0.48	28.50	1978	MPC01						

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT-- FORM (IN)		TEST SPECIMEN ORIENT (F)	YIELD STRENGTH (KSI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	2.5* (K(IC)/TVS)**2 (IN)	K(IC) MEAN (KSI*SQRT IN)	K(IC) STAN DEV (IN)	DATE	REFER
	THICK (IN)	THIN (IN)			WIDTH (IN)	THICK (IN)	DESIGN (IN)	A						
1851	P	2.35	R.T	64.3	3.001	1.499	CT	1.527	0.51	29.20	1980	RA001		
		4.25		64.4	3.008	1.500	CT	1.534	0.55	30.80	1978	MPCO1		
		3.00		64.4	2.975	1.636	CT	1.538	0.48	28.60	1978	MPCO1		
		2.00		64.4	3.016	1.499	CT	1.538	0.50	29.50	1978	MPCO1		
		4.50		64.4	3.024	1.500	CT	1.512	0.62	32.20	1978	MPCO1		
		1.12		64.4	3.000	1.140	CT	1.537	0.53	29.79	1980	RA001		
		1.50		64.9	2.990	1.493	CT	1.525	0.57	31.60	1978	MPCO1		
		4.25		64.5	3.008	1.500	CT	1.534	0.50	29.60	1978	MPCO1		
		2.50		64.5	3.004	1.498	CT	1.546	0.44	27.10	1980	RA001		
		2.50		64.5	2.010	0.998	CT	1.005	0.34	24.00	1978	MPCO1		
		2.50		64.5	2.510	1.249	CT	1.280	0.50	39.40	1978	MPCO1		
		2.50		64.5	2.999	1.494	CT	1.536	0.39	25.70	1980	RA001		
		4.25		64.5	2.498	1.230	CT	1.274	0.48	31.80	1978	MPCO1		
		4.25		64.7	3.026	1.499	CT	1.543	0.60	31.80	1978	MPCO1		
		2.50		64.7	3.014	1.102	CT	1.567	0.40	26.50	1978	MPCO1		
		2.75		64.7	3.024	1.500	CT	1.542	0.70	34.80	1978	MPCO1		
		4.25		64.7	3.028	1.501	CT	1.514	0.62	32.50	1978	MPCO1		
		3.00		64.8	3.000	1.499	CT	1.558	0.40	26.00	1979	RA001		
		2.00		64.8	3.002	1.496	CT	1.554	0.40	26.10	1980	RA001		
		2.20		64.8	3.001	1.498	CT	1.554	0.52	29.70	1980	RA001		
		2.50		64.9	2.010	1.000	CT	1.005	0.55	30.60	1978	MPCO1		
		2.50		64.9	2.508	1.250	CT	1.279	0.42	27.20	1978	MPCO1		
		2.50		64.9	2.486	1.250	CT	1.268	0.42	26.90	1978	MPCO1		
		3.25		64.9	3.016	1.497	CT	1.508	0.70	34.40	1978	MPCO1		
		1.81		64.9	2.982	1.493	CT	1.521	0.52	29.90	1978	MPCO1		
		2.75		64.9	2.997	1.498	CT	1.610	0.60	32.00	1980	RA001		
		4.90		65.0	3.000	1.500	CT	1.591	0.49	28.90	1978	RA002		
		2.00		65.0	3.017	1.499	CT	1.569	0.57	31.20	1978	MPCO1		
		0.62		65.0	1.006	0.500	CT	0.503	0.46	28.40	1978	MPCO1		
		1.50		65.1	3.000	1.479	CT	1.532	0.52	29.90	1980	RA001		
		2.00		65.1	3.000	1.476	CT	1.581	0.59	31.79	1980	RA001		
		4.00		65.2	3.979	2.000	CT	2.069	0.50	29.40	1978	MPCO1		
		2.50		65.2	2.008	0.899	CT	1.044	0.44	27.60	1978	MPCO1		
		2.50		65.2	2.999	1.498	CT	1.555	0.48	28.70	1980	RA001		
		1.75		65.2	2.999	1.500	CT	1.567	0.61	32.30	1972	B4368		
		1.57		65.2	3.000	1.500	CT	1.530	0.73	35.20	1978	MPCO1		
		3.00		65.2	3.008	1.400	CT	1.594	0.48	28.90	1978	MPCO1		
		1.57		65.2	3.000	1.500	CT	1.480	0.69	34.20	1972	B4368		
		3.00		65.2	2.001	0.997	CT	1.012	0.54	30.50	1978	RA002		

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM			SPECIMEN		CRACK LENGTH (IN)	2.5* CRACK LENGTH (K(1C)/TVS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV (IN)	DATE	REFER
	FORM	THICK (IN)			THICK (IN)	WIDTH (IN)	THICK (IN)	DESIGN (IN)							
T851	P	2.35	R. T.	L-Y	65.2	2.016	1.001	CT	0.988	0.40	26.70	1978	MPC01		
		4.00			65.2	4.039	1.977	CT	2.060	0.48	29.10	1978	MPC01		
		2.50			65.3	3.000	1.479	CT	1.522	0.45	28.00	1980	RA001		
		2.00			65.3	1.794	0.799	CT	1.017	0.42	27.30	1978	MPC01		
		2.50			65.4	2.000	1.000	CT	1.010	0.44	27.30	1972	84368		
		2.04			65.4	1.500	0.750	CT	0.740	0.27	21.30	1972	84368		
		2.50			65.4	2.000	1.000	CT	1.020	0.43	27.10	1972	84368		
		1.81			65.4	2.012	0.978	CT	1.046	0.44	27.60	1978	MPC01		
		2.00			65.4	3.003	1.501	CT	1.568	0.54	30.40	1978	RA002		
		3.50			65.4	3.000	1.500	CT	1.540	0.44	27.90	1972	84368		
		2.04			65.4	1.500	0.750	CT	0.750	0.26	21.10	1972	84368		
		3.00			65.4	2.775	1.245	CT	1.517	0.55	30.80	1978	MPC01		
		2.00			65.4	3.030	1.500	CT	1.515	0.48	29.00	1978	MPC01		
		2.50			65.4	2.970	1.478	CT	1.525	0.55	30.90	1978	MPC01		
		3.00			65.5	1.977	0.978	CT	1.014	0.59	32.00	1979	RA001		
		2.50			65.5	1.978	0.978	CT	0.979	0.50	29.90	1978	MPC01		
		4.00			65.5	3.000	1.500	CT	1.580	0.31	23.00	1972	84368		
		4.00			65.5	3.000	1.500	CT	1.560	0.30	22.50	1972	84368		
		2.50			65.6	4.000	2.000	CT	2.100	0.77	36.40	1972	84368		
		2.50			65.6	4.000	2.000	CT	2.100	0.77	36.40	1972	84368		
		3.00			65.6	3.001	1.478	CT	1.574	0.47	29.20	1978	RA001		
		5.50			65.7	3.018	1.500	CT	1.509	0.44	28.10	1978	MPC01		
		2.50			65.7	2.983	1.499	CT	1.551	0.42	27.00	1978	MPC01		
		1.12			65.7	3.018	1.435	CT	1.479	0.34	24.70	1978	MPC01		
		3.00			65.8	3.028	1.400	CT	1.605	0.62	33.10	1978	MPC01		
		1.75			65.9	3.003	1.501	CT	1.583	0.60	32.90	1978	RA002		
		2.40			65.9	3.003	1.478	CT	1.534	0.47	29.40	1980	RA001		
		2.25			66.0	2.016	0.979	CT	1.068	0.38	26.30	1978	MPC01		
1.50			66.0	3.000	1.500	CT	---	0.52	30.00	1982	MC003				
3.00			66.0	2.400	0.755	CT	1.356	0.60	32.40	1972	84306				
1.25			66.0	2.006	0.978	CT	1.083	0.44	28.20	1978	MPC01				
2.50			66.0	3.003	1.477	CT	1.520	0.51	30.10	1978	RA002				
1.50			66.1	3.000	1.500	CT	---	0.52	30.00	1982	MC003				
1.50			66.1	3.001	1.476	CT	1.564	0.54	31.00	1980	RA001				
2.50			66.2	4.000	2.000	CT	2.150	0.65	33.70	1972	84368				
2.50			66.2	4.000	2.000	CT	2.160	0.69	34.90	1972	84368				
2.00			66.2	3.000	1.500	CT	1.550	0.52	30.30	1972	84368				
1.50			66.2	3.018	1.478	CT	1.509	0.50	29.80	1978	MPC01				
1.12			66.2	2.004	1.000	CT	1.022	0.46	28.90	1978	MPC01				

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	L-T	SPECIMEN		CRACK LENGTH (IN)	K(KIC)	2.5* K(KIC)/TYS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	K(KIC) STAN DEV (IN)	DATE	REFER
	PRODUCT-- FORM (IN)	THICK (IN)					WIDTH (IN)	THICK (IN)							
1851	P	2.00	66.2	R T			1.500	CT	1.560	0.53	30.40		1972	84368	
		1.50	66.2				2.996	CT	1.528	0.46	29.00		1978	MPC01	
		0.87	66.2				1.500	CT	0.750	0.38	26.30		1978	MPC01	
		2.50	66.2				2.999	CT	1.539	0.45	28.20		1978	RA002	
		1.37	66.3				2.013	CT	1.067	0.34	25.10		1978	MPC01	
		2.25	66.3				3.018	CT	1.539	0.48	29.30		1978	MPC01	
		2.50	66.3				1.998	CT	1.021	0.36	25.50		1979	RA001	
		2.00	66.4				4.000	CT	---	0.54	30.90		1978	UD005	
		1.12	66.4				2.982	CT	1.461	0.34	29.00		1978	MPC01	
		2.00	66.4				2.000	CT	1.014	0.26	21.40		1972	84306	
		2.00	66.4				2.000	CT	1.018	0.34	24.60		1972	84306	
		2.00	66.4				4.000	CT	---	0.51	30.10		1978	UD005	
		1.75	66.4				3.003	CT	1.563	0.52	30.40		1972	84306	
		2.00	66.4				2.000	CT	1.259	0.39	24.70		1978	RA002	
		2.50	66.4				1.994	CT	1.057	0.38	26.10		1978	MPC01	
		2.00	66.4				4.000	CT	---	0.52	30.40		1978	UD005	
		1.50	66.5				2.998	CT	1.541	0.50	29.79		1978	RA001	
		2.00	66.6				2.983	CT	1.581	0.57	32.20		1978	MPC01	
		2.75	66.6				3.002	CT	1.561	0.50	30.00		1978	RA002	
		1.12	66.7				3.017	CT	1.599	0.48	29.80		1978	MPC01	
		2.50	66.7				3.024	CT	1.542	0.42	27.80		1978	MPC01	
		0.87	66.7				1.504	CT	0.752	0.46	28.90		1978	MPC01	
		1.55	66.7				3.000	CT	1.487	0.42	27.50		1980	RA001	
		1.62	66.7				3.001	CT	1.575	0.49	28.60		1978	RA002	
		3.00	66.9				3.015	CT	1.628	0.62	33.50		1978	MPC01	
		2.25	66.9				3.019	CT	1.598	0.48	29.80		1978	MPC01	
		1.75	67.0				3.000	CT	1.580	0.49	28.30		1972	84368	
		3.00	67.0				2.993	CT	1.616	0.67	35.10		1978	MPC01	
		1.55	67.0				2.978	CT	1.489	0.44	28.70		1978	MPC01	
		1.50	67.0				3.030	CT	1.515	0.40	27.30		1978	MPC01	
		1.75	67.0				3.012	CT	1.506	0.40	27.20		1978	MPC01	
		1.75	67.0				3.000	CT	1.570	0.45	28.60		1972	84368	
		1.73	67.1				2.999	CT	1.536	0.48	29.60		1978	RA002	
		1.75	67.1				3.011	CT	1.626	0.42	27.80		1978	MPC01	
		1.57	67.2				3.000	CT	1.560	0.37	26.00		1972	84368	
		1.75	67.2				3.003	CT	1.587	0.48	29.50		1980	RA001	
		2.03	67.2				2.982	CT	1.521	0.55	31.70		1978	MPC01	
		2.03	67.2				2.998	CT	1.529	0.60	33.50		1978	MPC01	
		1.57	67.2				3.000	CT	1.560	0.39	26.50		1972	84368	

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	SPECIMEN DESIGN	CRACK LENGTH (IN)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER		
	FORM	PRODUCT-- THICK (IN)												
T851	P	1.50	67.2	2.509	1.252	CT	1.282	0.45	28.79		1981	MA002		
		1.50	67.2	2.512	1.253	CT	1.298	0.46	29.00		1981	MA002		
		1.50	67.6	2.997	1.494	CT	1.525	0.45	28.79		1978	RA001		
		1.55	67.7	3.000	1.501	CT	1.575	0.38	26.50		1979	RA001		
		2.00	67.7	3.029	1.498	CT	1.545	0.44	28.60		1978	MFC01		
		1.55	67.8	1.998	0.999	CT	1.019	0.40	27.70		1978	MFC01		
		1.50	67.9	1.985	0.999	CT	1.032	0.42	28.00		1978	MFC01		
		1.75	68.0	2.998	1.498	CT	1.589	0.55	32.40		1978	MFC01		
		1.37	68.2	2.984	1.376	CT	1.462	0.38	26.90		1978	MFC01		
		1.25	68.4	2.017	0.999	CT	1.089	0.38	26.90		1978	MFC01		
		1.73	68.4	3.003	1.503	CT	1.611	0.48	30.20		1978	RA002		
		1.62	68.8	3.001	1.451	CT	1.522	0.40	27.79		1978	RA001		
		1.50	69.1	3.002	1.492	CT	1.528	0.36	26.70		1980	RA001		
		1.75	69.5	2.998	1.500	CT	1.559	0.44	29.20		1978	MFC01		
		2.52	69.7	2.000	1.000	CT	0.960	0.34	25.50		1972	84368		
		2.52	69.7	2.000	1.000	CT	0.960	0.35	26.00		1972	84368		
		2.52	69.7	2.000	1.000	CT	0.940	0.33	25.20	29.7/	2.8	1972	84368	
	T851	P	3.50	64.4	3.000	1.500	CT	1.547	0.45	27.40	28.5/	1.6	1973	86213
			3.50	64.4	3.000	1.499	CT	1.533	0.53	29.60			1973	86213
	T851	P	2.50	56.9	2.000	1.000	CT	---	0.85	33.30		1974	88742	
		2.50	56.9	2.000	1.000	CT	---	0.88	33.90		1974	88742		
		2.50	56.9	2.000	1.000	CT	---	0.78	31.90	33.0/	1.0	1974	88742	
T851	P	3.00	---	3.014	1.372	CT	1.477	---	26.40		1978	MFC01		
		5.00	53.0	3.004	1.502	CT	1.533	0.56	25.10		1979	GD011		
		6.00	53.9	3.020	1.499	CT	1.510	0.44	23.10		1978	MFC01		
		5.50	54.2	2.973	1.497	CT	1.516	0.50	24.80		1978	MFC01		
		5.25	54.4	2.998	1.498	CT	1.559	0.50	24.80		1978	MFC01		
		6.00	54.6	2.979	1.499	CT	1.579	0.57	26.60		1978	MFC01		
		5.25	54.9	3.012	1.499	CT	1.536	0.42	22.90		1978	MFC01		
		6.00	54.9	3.008	1.499	CT	1.594	0.55	26.00		1978	MFC01		
		6.00	54.9	2.985	1.499	CT	1.552	0.67	28.80		1978	MFC01		
		6.00	55.0	3.000	1.500	CT	1.580	0.48	24.10		1972	84368		
		6.00	55.0	3.000	1.500	CT	1.560	0.46	23.70		1972	84368		
		5.50	55.6	3.017	1.498	CT	1.569	0.70	29.90		1978	MFC01		
		5.50	55.9	2.999	1.500	CT	1.582	0.50	25.00		1980	RA001		
		5.75	56.4	2.001	0.995	CT	1.010	0.60	27.70		1980	RA001		

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	R. T.	T-L	SPECIMEN		CRACK LENGTH (IN)	K (IC)	2.5* (K(IC)/TYS)**2 (IN)	K (IC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)					WIDTH (IN)	THICK (IN)							
T851	P	5	50				M	B	A						
		6	00	56.5			3.008	1.499	CT	1.564	0.55	27.00		1978	MPC01
		5	50	56.7			3.004	1.499	CT	1.622	0.50	26.00		1978	MPC01
		5	50	56.7			3.028	1.500	CT	1.544	0.48	25.10		1978	MPC01
		5	50	56.8			3.010	1.498	CT	1.505	0.57	27.60		1978	MPC01
		6	00	57.0			2.001	0.998	CT	1.000	0.56	27.20		1980	RA001
		6	00	57.0			3.014	1.498	CT	1.537	0.38	22.30		1978	MPC01
		5	00	57.0			3.010	1.498	CT	1.505	0.44	24.10		1978	MPC01
		5	00	57.0			3.026	1.500	CT	1.604	0.42	23.90		1978	MPC01
		4	90	57.1			3.000	1.498	CT	1.556	0.73	30.90		1978	RA002
		6	00	57.1			3.026	1.474	CT	1.513	0.57	27.90		1978	MPC01
		5	12	57.1			3.028	1.499	CT	1.544	0.55	27.20		1978	MPC01
		5	00	57.2			2.996	1.497	CT	1.528	0.60	28.30		1978	MPC01
		5	12	57.3			2.987	1.500	CT	1.583	0.70	30.50		1978	MPC01
		4	62	57.4			2.981	1.500	CT	1.550	0.60	28.50		1978	MPC01
		5	50	57.7			3.008	1.502	CT	1.564	0.36	22.40		1978	MPC01
		5	50	57.7			2.994	1.500	CT	1.557	0.44	24.40		1978	MPC01
		5	00	57.8			2.998	1.501	CT	1.585	0.51	26.29		1979	RA001
		5	00	57.8			2.006	0.998	CT	1.043	0.46	25.30		1978	MPC01
		6	00	57.9			1.998	0.997	CT	1.025	0.47	25.27		1978	RA001
		4	62	57.9			3.020	1.499	CT	1.510	0.42	24.20		1978	MPC01
		4	50	58.0			2.997	1.497	CT	1.548	0.47	25.40		1979	RA001
		5	50	58.0			2.986	1.500	CT	1.463	0.48	26.00		1978	MPC01
		5	50	58.1			3.006	1.501	CT	1.533	0.38	22.80		1978	MPC01
		5	50	58.2			2.984	1.498	CT	1.492	0.52	27.00		1978	MPC01
		5	00	58.4			3.001	1.498	CT	1.612	0.44	24.60		1978	RA001
		4	25	58.4			3.000	1.499	CT	1.599	0.48	25.60		1980	RA001
		5	00	58.4			2.996	1.499	CT	1.533	0.40	23.40		1979	RA001
		5	00	58.5			3.020	1.498	CT	1.540	0.40	23.50		1978	MPC01
		4	50	58.5			3.000	1.500	CT	1.570	0.51	26.90		1972	8436B
		4	00	58.5			2.999	1.498	CT	1.560	0.43	24.27		1980	RA001
		5	50	58.6			2.996	1.501	CT	1.528	0.44	25.10		1978	MPC01
		5	00	58.6			2.972	1.499	CT	1.605	0.44	24.80		1978	MPC01
	5	25	58.6			3.018	1.499	CT	1.509	0.52	27.20		1978	MPC01	
	4	00	58.7			1.998	0.998	CT	1.005	0.36	22.50		1979	RA001	
	5	50	58.7			2.982	1.500	CT	1.521	0.44	25.20		1978	MPC01	
	5	50	58.8			3.031	1.500	CT	1.546	0.36	22.70		1978	MPC01	
	5	50	58.8			3.008	1.500	CT	1.534	0.30	21.00		1978	MPC01	
	4	90	58.9			3.000	1.499	CT	1.623	0.40	23.79		1978	RA002	
	4	00	58.9			3.006	1.492	CT	1.533	0.48	26.40		1978	MPC01	

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	R	T	T-L	SPECIMEN		CRACK LENGTH (IN)	K(1C)	2 S* (IN)	K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	PRODUCT-- FORM	THICK (IN)							WIDTH (IN)	THICK (IN)								
1851	P	4.55	58.9						M	B	A							1980 RA001
		4.00	58.9						3.001	1.500	CT	1.563	0.57		28.20		1978 MPC01	
		6.00	59.0						2.987	1.500	CT	1.589	0.38		23.00		1978 MPC01	
		4.00	59.0						3.012	1.501	CT	1.553	0.62		29.50		1978 MPC01	
		5.50	59.0						2.977	1.501	CT	1.566	0.42		24.50		1978 MPC01	
		5.50	59.1						3.006	1.500	CT	1.548	0.48		26.50		1978 MPC01	
		4.90	59.1						3.006	1.493	CT	1.533	0.40		23.70		1978 MPC01	
		4.50	59.1						2.994	1.498	CT	1.503	0.44		25.30		1978 MPC01	
		4.90	59.1						3.000	1.499	CT	1.587	0.55		28.20		1978 MPC01	
		4.00	59.1						3.000	1.498	CT	1.613	0.47		25.79		1978 RA002	
		5.50	59.2						3.028	1.500	CT	1.604	0.56		28.10		1980 RA001	
		4.50	59.2						2.987	1.498	CT	1.544	0.36		22.80		1978 MPC01	
		4.50	59.2						3.017	1.498	CT	1.553	0.38		22.80		1978 MPC01	
		4.00	59.2						3.004	1.499	CT	1.599	0.55		28.20		1978 MPC01	
		5.50	59.2						2.983	1.497	CT	1.562	0.34		22.40		1978 MPC01	
		5.50	59.3						3.000	1.500	CT	1.551	0.30		21.00		1978 MPC01	
		6.00	59.3						2.976	1.500	CT	1.510	0.34		21.80		1972 84368	
		5.50	59.3						3.000	1.500	CT	1.577	0.60		29.60		1978 MPC01	
		4.50	59.4						3.001	1.501	CT	1.540	0.35		22.30		1972 84368	
		5.50	59.6						3.016	1.500	CT	1.583	0.36		22.79		1978 RA002	
		5.50	59.6						3.016	1.499	CT	1.538	0.32		21.50		1978 MPC01	
		5.50	59.6						3.008	1.502	CT	1.538	0.30		20.90		1978 MPC01	
		5.00	59.7						2.000	1.001	CT	1.534	0.32		21.90		1978 MPC01	
		5.50	59.8						3.026	1.500	CT	1.045	0.37		23.20		1978 RA002	
		5.50	59.8						3.018	1.500	CT	1.943	0.38		23.50		1978 MPC01	
		5.50	59.8						2.996	1.500	CT	1.539	0.40		24.20		1978 MPC01	
		6.00	59.9						3.012	1.499	CT	1.558	0.40		24.10		1978 MPC01	
		4.90	60.0						3.003	1.500	CT	1.570	0.38		23.40		1980 RA001	
	4.00	60.0						2.000	1.000	CT	1.566	0.65		30.60		1978 MPC01		
	4.50	60.0						3.000	1.500	CT	1.572	0.42		24.60		1978 RA002		
	4.50	60.0						3.000	1.496	CT	1.030	0.37		28.80		1972 84368		
	5.50	60.1						2.994	1.501	CT	1.604	0.41		24.29		1978 RA002		
	4.00	60.1						2.999	1.500	CT	1.557	0.34		22.50		1978 MPC01		
	5.50	60.1						3.000	1.501	CT	1.493	0.54		28.10		1980 RA001		
	5.50	60.1						3.002	1.500	CT	1.530	0.38		23.80		1978 MPC01		
	5.25	60.1						3.026	1.500	CT	1.527	0.32		22.10		1978 MPC01		
	5.50	60.1						2.992	1.500	CT	1.513	0.44		25.30		1978 MPC01		
																		1978 MPC01

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	R. T.	T-L	SPECIMEN		WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(1C) (KSI)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER	
	FORM	THICK (IN)						M	B											A
1B51	P	4.00	60.2	3.000	1.497	CT	1.636	24.40	0.41	1978	RA001									
		5.50	60.2	2.988	1.500	CT	1.524	22.90	0.36	1978	MPC01									
		4.00	60.3	3.020	1.498	CT	1.540	27.20	0.50	1978	MPC01									
		4.25	60.3	1.981	0.997	CT	1.030	26.40	0.46	1978	MPC01									
		4.00	60.4	2.998	1.373	CT	1.588	27.40	0.51	1978	RA001									
		5.50	60.4	3.000	1.500	CT	1.500	23.30	0.36	1978	MPC01									
		5.00	60.4	3.214	1.499	CT	1.539	23.40	0.36	1978	MPC01									
		5.50	60.4	2.978	1.500	CT	1.519	23.60	0.38	1978	MPC01									
		3.50	60.4	3.016	1.497	CT	1.478	26.50	0.46	1978	MPC01									
		5.50	60.6	2.998	1.500	CT	1.529	21.20	0.28	1978	MPC01									
		5.25	60.6	3.018	1.500	CT	1.539	27.70	0.50	1978	MPC01									
		1.81	60.6	3.002	1.498	CT	1.651	25.70	0.44	1978	MPC01									
		3.75	60.6	2.996	1.497	CT	1.528	27.00	0.48	1978	MPC01									
		5.50	60.6	3.014	1.500	CT	1.537	23.50	0.36	1978	MPC01									
		5.50	60.6	2.996	1.500	CT	1.528	23.00	0.34	1978	MPC01									
		5.50	60.6	3.018	1.500	CT	1.539	22.20	0.32	1978	MPC01									
		4.50	60.7	3.020	1.501	CT	1.510	26.70	0.46	1978	MPC01									
		4.31	60.8	2.000	1.000	CT	1.000	23.60	0.38	1972	84368									
		4.31	60.8	2.000	1.000	CT	0.990	23.90	0.39	1972	84368									
		5.00	60.9	2.988	1.500	CT	1.524	21.90	0.30	1978	MPC01									
		3.00	60.9	3.002	1.498	CT	1.567	29.29	0.57	1980	RA001									
		4.00	60.9	2.998	1.499	CT	1.608	25.29	0.43	1979	RA001									
		5.00	61.0	3.020	1.501	CT	1.631	26.60	0.46	1978	MPC01									
		5.50	61.1	3.004	1.418	CT	1.559	28.50	0.54	1980	RA001									
		4.00	61.1	3.000	1.498	CT	1.552	22.00	0.32	1978	MPC01									
		5.25	61.1	2.985	1.500	CT	1.562	29.70	0.59	1978	RA001									
		3.00	61.1	2.999	1.498	CT	1.546	26.29	0.46	1978	MPC01									
		5.50	61.1	2.988	1.501	CT	1.524	22.50	0.32	1978	MPC01									
		6.00	61.1	3.008	1.499	CT	1.594	31.80	0.67	1978	MPC01									
		4.25	61.1	3.020	1.500	CT	1.540	22.70	0.34	1978	MPC01									
		1.75	61.3	2.999	1.499	CT	1.563	24.70	0.40	1980	RA001									
		4.90	61.3	3.000	1.499	CT	1.623	25.79	0.44	1978	RA002									
		4.50	61.4	3.000	1.500	CT	1.570	23.30	0.36	1972	84368									
		4.50	61.4	3.000	1.500	CT	1.520	22.50	0.34	1972	84368									
		5.50	61.4	3.010	1.500	CT	1.539	22.30	0.32	1978	MPC01									
		4.50	61.4	3.030	1.500	CT	1.515	28.60	0.52	1978	MPC01									
		4.50	61.4	3.020	1.500	CT	1.510	27.70	0.50	1978	MPC01									
		3.00	61.4	3.001	1.438	CT	1.613	25.40	0.42	1978	RA001									

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	THICK (IN)	SPECIMEN		CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER
	FORM	W					B	DESIGN						
T851	P	5 00	61 4	T-L	R T	3 028	1 500	CT	1 544	0 32	22 30		1978	MPC01
		5 50	61 4			3 006	1 500	CT	1 533	0 28	21 30		1978	MPC01
		4 50	61 4			3 014	1 500	CT	1 507	0 50	27 90		1978	MPC01
		4 00	61 4			3 000	1 497	CT	1 657	0 50	27 70		1979	RA001
		3 50	61 5			3 000	1 497	CT	1 602	0 55	29 00		1978	RA001
		4 31	61 5			3 022	1 502	CT	1 632	0 42	25 90		1978	MPC01
		5 00	61 5			3 000	1 499	CT	1 547	0 37	23 70		1980	RA001
		2 25	61 6			2 994	1 502	CT	1 587	0 52	28 80		1978	MPC01
		3 50	61 6			3 006	1 499	CT	1 533	0 50	28 30		1978	MPC01
		4 90	61 6			3 030	1 494	CT	1 515	0 38	24 30		1978	MPC01
		5 50	61 6			3 029	1 500	CT	1 549	0 32	22 60		1978	MPC01
		3 50	61 6			2 990	1 497	CT	1 555	0 52	28 40		1978	MPC01
		4 25	61 6			2 990	1 500	CT	1 529	0 32	22 30		1978	MPC01
		4 00	61 7			2 994	1 499	CT	1 587	0 38	24 40		1978	MPC01
		3 00	61 7			2 994	1 499	CT	1 031	0 37	24 00		1979	RA001
		5 00	61 7			2 994	1 500	CT	1 562	0 34	23 00		1978	MPC01
		3 00	61 7			2 994	1 404	CT	1 556	0 51	28 10		1980	RA001
		2 70	61 7			2 017	0 999	CT	1 049	0 55	29 30		1978	MPC01
		3 00	61 8			3 002	1 374	CT	1 505	0 37	23 79		1980	RA001
		2 50	61 8			2 994	1 056	CT	1 557	0 38	24 90		1978	MPC01
		4 25	61 9			3 000	1 499	CT	1 647	0 42	25 60		1978	RA001
		5 50	61 9			3 026	1 502	CT	1 543	0 32	22 90		1978	MPC01
		3 12	61 9			3 000	1 500	CT	2 100	0 44	26 00		1978	GD003
		5 50	61 9			3 022	1 499	CT	1 511	0 50	27 90		1978	MPC01
		5 50	61 9			3 000	1 500	CT	2 100	0 43	25 70		1978	GD003
		5 50	61 9			3 000	1 500	CT	2 100	0 43	25 70		1978	GD003
		4 25	61 9			3 002	1 499	CT	1 561	0 28	21 60		1978	RA002
		3 62	62 0			2 995	1 498	CT	1 544	0 34	22 90		1980	RA001
	2 00	62 0			2 994	1 499	CT	1 597	0 53	28 70		1980	RA001	
	4 25	62 1			2 978	1 500	CT	1 519	0 36	24 00		1978	MPC01	
	4 50	62 1			3 006	1 500	CT	1 533	0 50	28 20		1978	MPC01	
	4 50	62 1			3 006	1 500	CT	1 503	0 55	29 40		1978	MPC01	
	4 50	62 1			2 994	1 501	CT	1 527	0 50	28 30		1978	MPC01	
	4 50	62 1			3 002	1 498	CT	1 600	0 48	27 40		1980	RA001	
	2 50	62 1			2 000	1 000	CT	---	0 47	26 70		1974	BB742	
	2 00	62 1			2 002	1 002	CT	1 052	0 32	22 29		1978	RA002	
	4 90	62 1			3 000	1 500	CT	1 617	0 40	25 10		1978	RA002	
	2 50	62 1			2 000	1 000	CT	---	0 47	26 90		1974	BB742	

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	K(IIC) (KSI)	2.5* (K(IIC)/TYS)**2 (IN)	K(IIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
						WIDTH (IN)	THICK (IN)	DESIGN	A							
						H	B									
1851	P	4.50	R	T	62.1	3.016	1.500	CT	1.508	0.50	28.10	1978	MPC01			
		2.50		T-L	62.1	2.000	1.000	CT	---	0.52	28.20	1974	88742			
		2.50			62.2	3.021	0.869	CT	1.420	0.40	25.40	1978	MPC01			
		1.73			62.3	1.992	1.000	CT	1.016	0.36	24.10	1978	MPC01			
		3.50			62.3	3.001	1.500	CT	1.581	0.45	26.60	1979	RA001			
		2.50			62.3	2.989	1.498	CT	1.584	0.36	24.10	1978	MPC01			
		3.00			62.3	3.002	1.375	CT	1.951	0.61	31.00	1980	RA001			
		2.50			62.3	2.000	0.997	CT	1.040	0.30	21.90	1978	MPC01			
		4.00			62.4	3.002	1.251	CT	1.644	0.33	22.70	1980	RA001			
		5.50			62.4	2.988	1.499	CT	1.524	0.48	27.70	1978	MPC01			
		2.50			62.4	2.964	1.500	CT	1.926	0.42	25.70	1980	RA001			
		3.12			62.4	3.003	1.498	CT	1.565	0.50	28.10	1980	RA001			
		1.50			62.4	3.000	1.484	CT	1.556	0.42	25.60	1980	RA001			
		4.25			62.4	3.020	1.500	CT	1.540	0.34	23.10	1978	MPC01			
		3.00			62.4	3.008	1.482	CT	1.504	0.42	26.10	1978	MPC01			
		3.00			62.5	2.999	1.363	CT	1.568	0.35	23.60	1980	RA001			
		3.00			62.5	3.001	1.187	CT	1.641	0.39	25.00	1978	RA002			
		4.25			62.5	2.986	1.500	CT	1.523	0.34	23.30	1978	MPC01			
		2.75			62.5	3.000	1.496	CT	1.648	0.35	23.40	1978	RA002			
		4.50			62.6	3.012	1.501	CT	1.506	0.44	26.80	1978	MPC01			
		2.50			62.6	3.000	1.499	CT	1.592	0.41	25.60	1978	RA002			
		3.00			62.6	2.999	1.301	CT	1.515	0.43	26.30	1978	RA002			
		3.50			62.6	3.000	1.498	CT	1.559	0.39	23.60	1980	RA001			
		4.00			62.7	3.019	1.500	CT	1.630	0.42	26.10	1978	MPC01			
		3.50			62.7	3.000	1.500	CT	1.550	0.46	26.80	1972	84368			
		4.00			62.7	3.002	1.498	CT	1.591	0.46	27.20	1978	MPC01			
		3.50			62.7	3.000	1.500	CT	1.550	0.44	26.40	1972	84368			
		3.12			62.7	3.000	1.498	CT	1.594	0.54	29.40	1978	RA001			
		3.00			62.8	3.014	1.301	CT	1.567	0.46	27.20	1978	MPC01			
		3.00			62.8	3.000	1.498	CT	1.505	0.32	22.60	1980	RA001			
		4.25			62.8	2.977	1.500	CT	1.518	0.34	23.40	1978	MPC01			
		3.00			62.9	2.999	1.399	CT	1.523	0.59	29.70	1980	RA001			
		2.00			62.9	3.026	1.503	CT	1.513	0.38	25.00	1978	MPC01			
		5.00			62.9	2.981	1.500	CT	1.550	0.38	24.70	1978	MPC01			
		3.12			62.9	2.980	1.448	CT	1.609	0.48	28.20	1978	MPC01			
		4.25			62.9	2.990	1.500	CT	1.525	0.38	21.80	1978	MPC01			
		4.25			62.9	3.014	1.500	CT	1.537	0.36	24.00	1978	MPC01			
		2.00			62.9	3.016	1.497	CT	1.508	0.40	25.30	1978	MPC01			
		3.62			62.9	3.031	1.497	CT	1.485	0.40	25.20	1978	MPC01			

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN		W	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(1C)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) STAN (KSI*SQRT IN)	DATE	REFER					
	FORM	THICK (IN)		ORIENT	TEMP (F)										R. T.	T-L	THICK (IN)		K(1C) MEAN (IN)
																	A	B	
T851	P	2.50	63.0	2.489	1.250	CT	1.294	0.40	25.70	1978	MPC01								
		2.50	63.0	2.528	1.250	CT	1.289	0.40	25.50	1978	MPC01								
		3.54	63.0	3.019	1.498	CT	1.630	0.46	27.40	1978	MPC01								
		2.50	63.1	2.998	1.099	CT	1.589	0.36	24.20	1978	MPC01								
		4.25	63.2	2.975	1.500	CT	1.547	0.32	22.90	1978	MPC01								
		1.75	63.2	2.980	1.498	CT	1.490	0.28	22.00	1978	MPC01								
		3.00	63.2	2.000	0.995	CT	1.036	0.41	25.90	1978	RA002								
		3.25	63.4	3.027	1.499	CT	1.574	0.42	26.30	1978	MPC01								
		2.25	63.4	2.985	1.503	CT	1.582	0.44	27.20	1978	MPC01								
		4.25	63.4	2.983	1.499	CT	1.551	0.30	22.80	1978	MPC01								
		5.50	63.4	2.988	1.500	CT	1.524	0.32	22.90	1978	MPC01								
		1.37	63.4	1.996	0.998	CT	1.078	0.30	22.20	1978	MPC01								
		2.50	63.5	3.001	1.496	CT	1.572	0.37	25.40	1980	RA001								
		2.00	63.5	2.990	1.499	CT	1.555	0.32	23.40	1978	MPC01								
		2.35	63.5	3.000	1.499	CT	1.541	0.39	24.00	1980	RA001								
		3.12	63.6	3.027	1.499	CT	1.574	0.42	26.30	1978	MPC01								
		2.50	63.6	3.001	1.499	CT	1.600	0.37	25.40	1978	RA002								
		3.00	63.7	3.001	1.333	CT	1.574	0.33	23.40	1979	RA001								
		2.90	63.7	2.992	0.996	CT	1.466	0.42	26.30	1978	MPC01								
		3.54	63.7	3.000	1.497	CT	1.530	0.42	26.90	1978	MPC01								
		3.00	63.7	3.004	1.400	CT	1.592	0.32	23.30	1978	MPC01								
		2.75	63.8	2.999	1.498	CT	1.572	0.36	24.29	1980	RA001								
		2.50	63.8	3.028	1.498	CT	1.544	0.36	24.30	1978	MPC01								
		3.12	63.9	3.020	1.502	CT	1.480	0.46	27.60	1978	MPC01								
		2.00	63.9	2.990	0.870	CT	1.465	0.34	24.20	1978	MPC01								
		2.00	63.9	2.975	1.502	CT	1.517	0.44	27.20	1978	MPC01								
		1.75	64.0	3.001	1.498	CT	1.554	0.33	23.29	1978	RA001								
		5.00	64.1	2.989	1.499	CT	1.614	0.44	27.10	1978	MPC01								
		3.00	64.1	1.998	0.998	CT	1.029	0.41	26.00	1979	RA001								
		3.00	64.1	3.001	1.428	CT	1.591	0.43	26.60	1978	RA001								
		1.25	64.1	2.016	0.999	CT	1.028	0.34	23.80	1978	MPC01								
		2.50	64.1	2.999	1.498	CT	1.545	0.41	26.20	1980	RA001								
		2.75	64.2	3.000	1.496	CT	1.570	0.47	27.90	1980	RA001								
		3.50	64.2	3.000	1.500	CT	1.520	0.33	23.30	1972	84368								
		2.75	64.2	2.987	1.497	CT	1.553	0.44	27.30	1978	MPC01								
		3.00	64.2	3.017	1.496	CT	1.539	0.44	27.50	1978	MPC01								
		4.00	64.2	3.975	1.999	CT	2.067	0.42	26.60	1978	MPC01								
		3.50	64.2	3.000	1.500	CT	1.520	0.32	22.80	1972	84368								

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	K(IC) 2.5*	K(IC) MEAN DEV (KSI*SQRT IN)	K(IC) STAN DEV	DATE	REFER
	FORM	THICK (IN)			THICK (IN)	THICK (IN)	DESIGN	DESIGN						
T851	P	4.00	R. T.	64.2	3.000	1.500	CT	1.590	0.26	20.80			1972	84368
		0.62		64.2	1.004	0.500	CT	0.512	0.46	28.00			1978	MPC01
		3.00		64.2	2.996	1.400	CT	1.648	0.34	24.20			1978	MPC01
		2.50		64.2	2.000	1.000	CT	1.040	0.42	26.30			1972	84368
		4.00		64.2	3.000	1.500	CT	1.590	0.27	21.00			1972	84368
		1.75		64.2	2.998	1.501	CT	1.588	0.44	27.20			1980	RA001
		4.00		64.2	4.004	2.000	CT	2.042	0.42	26.40			1978	MPC01
		1.75		64.2	2.996	0.751	CT	1.498	0.30	22.90			1978	MPC01
		2.50		64.2	3.001	1.497	CT	1.564	0.30	22.60			1980	RA001
		2.75		64.2	3.002	1.373	CT	1.539	0.39	25.60			1980	RA001
		2.00		64.2	3.003	1.495	CT	1.533	0.30	22.50			1980	RA001
		2.50		64.2	2.000	1.000	CT	1.050	0.41	26.10			1972	84368
		2.50		64.4	4.000	2.000	CT	2.170	0.54	29.90			1972	84368
		3.62		64.4	2.987	1.501	CT	1.643	0.30	22.80			1978	MPC01
		2.50		64.4	4.000	2.000	CT	2.180	0.54	30.00			1972	84368
		2.00		64.4	2.993	1.499	CT	1.616	0.36	25.00			1978	MPC01
		3.25		64.4	3.030	1.498	CT	1.515	0.38	25.60			1978	MPC01
		2.00		64.4	3.000	1.498	CT	1.551	0.41	26.10			1980	RA001
		3.00		64.4	3.007	1.400	CT	1.624	0.36	25.00			1978	MPC01
		1.50		64.5	3.002	1.499	CT	1.512	0.36	24.79			1980	RA001
		1.75		64.5	3.004	1.500	CT	1.500	0.36	24.60			1978	RA002
		2.50		64.6	3.031	1.499	CT	1.576	0.32	23.40			1978	MPC01
		2.20		64.6	3.003	1.498	CT	1.576	0.35	24.20			1980	RA001
		2.50		64.6	2.998	1.500	CT	1.558	0.37	25.10			1980	RA001
		2.00		64.7	1.990	0.753	CT	1.029	0.32	23.20			1972	84306
		2.00		64.7	1.990	0.751	CT	1.004	0.29	21.90			1972	84306
		2.00		64.7	2.000	0.751	CT	1.038	0.33	23.40			1972	84306
		2.50		64.8	2.489	1.290	CT	1.294	0.44	27.30			1978	MPC01
		2.50		64.8	4.000	2.000	CT	2.130	0.46	27.70			1972	84368
		2.50		64.8	2.522	1.250	CT	1.286	0.42	27.10			1978	MPC01
		2.50		64.8	4.000	2.000	CT	2.150	0.47	28.10			1972	84368
		2.00		64.8	3.011	1.499	CT	1.596	0.42	27.00			1978	MPC01
		2.50		64.9	2.012	0.999	CT	0.986	0.25	21.10			1978	MPC01
		2.35		64.9	3.001	1.500	CT	1.546	0.36	24.79			1978	RA002
		3.54		64.9	3.016	1.504	CT	1.508	0.48	28.70			1978	MPC01
		2.25		64.9	1.996	0.998	CT	1.508	0.30	23.00			1978	MPC01
		2.35		65.0	2.018	1.009	CT	1.009	0.32	23.80			1978	MPC01
		2.50		65.1	2.037	0.998	CT	0.986	0.30	23.00			1978	MPC01
		3.00		65.1	2.988	1.247	CT	1.464	0.32	23.60			1978	MPC01

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT-- FORM		TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	SPECIMEN		CRACK LENGTH (IN)	2.5* (K(1C)/TVS)**2 (IN)	K(1C) STAN DEV (KBI*SQRT IN)	DATE	REFER
	THICK (IN)	THICK (IN)					THICK A	THICK B					
1851	P	1.12	R.T.	T-L	65.2	2.972	1.153	CT	1.486	0.28	22.20	1978	MPC01
		2.04			65.2	1.500	0.750	CT	0.740	0.22	19.30	1972	84368
		2.04			65.2	1.500	0.750	CT	0.730	0.22	19.40	1972	84368
		3.00			65.2	2.998	1.400	CT	1.619	0.38	26.00	1978	MPC01
		1.50			65.2	3.000	1.493	CT	1.500	0.38	26.00	1978	MPC01
		2.00			65.2	3.018	1.500	CT	1.509	0.38	25.80	1978	MPC01
		1.57			65.2	3.000	1.500	CT	1.520	0.51	29.40	1972	84368
		1.57			65.2	3.000	1.500	CT	1.540	0.54	30.30	1972	84368
		3.12			65.2	3.023	1.497	CT	1.602	0.44	27.70	1978	MPC01
		1.12			65.3	3.029	1.136	CT	1.484	0.27	22.10	1978	MPC01
		2.50			65.3	2.018	0.999	CT	1.009	0.55	30.80	1978	MPC01
		1.50			65.4	2.996	1.478	CT	1.528	0.42	27.10	1978	MPC01
		2.00			65.4	3.000	1.500	CT	1.540	0.34	24.10	1972	84368
		1.75			65.4	3.028	1.499	CT	1.514	0.38	25.80	1978	MPC01
		2.00			65.4	3.000	1.500	CT	1.540	0.35	24.40	1972	84368
		1.50			65.4	3.020	1.441	CT	1.540	0.42	27.20	1978	MPC01
		1.75			65.4	3.003	1.502	CT	1.568	0.40	26.20	1978	RA002
		1.50			65.4	2.999	1.478	CT	1.531	0.37	25.40	1980	RA001
		2.40			65.4	3.001	1.497	CT	1.554	0.32	23.70	1980	RA001
		2.50			65.4	3.000	1.500	CT	1.551	0.38	25.79	1980	RA001
		1.62			65.4	3.001	1.500	CT	1.558	0.38	25.90	1978	RA002
		2.00			65.5	1.994	0.899	CT	1.057	0.32	24.00	1976	MPC01
		2.00			65.6	3.001	1.500	CT	1.561	0.33	23.90	1978	RA002
		1.81			65.6	2.015	0.999	CT	1.048	0.32	24.10	1978	MPC01
		1.75			65.7	3.000	1.500	CT	1.560	0.33	24.00	1972	84368
		3.12			65.7	2.981	1.400	CT	1.580	0.34	24.90	1978	MPC01
		1.75			65.7	3.000	1.500	CT	1.580	0.33	23.90	1972	84368
		2.03			65.7	3.014	1.501	CT	1.537	0.46	28.70	1978	MPC01
		2.50			65.7	2.973	1.099	CT	1.546	0.28	22.80	1978	MPC01
		2.00			65.7	3.000	1.497	CT	1.564	0.34	24.50	1978	RA001
		0.87			65.8	1.502	0.750	CT	0.766	0.40	26.90	1978	MPC01
		0.87			65.8	1.508	0.750	CT	0.769	0.34	24.60	1978	MPC01
		2.50			65.8	2.999	1.499	CT	1.579	0.32	23.70	1978	RA002
		2.50			65.8	3.002	1.100	CT	1.528	0.31	23.40	1980	RA001
		2.25			65.8	2.002	0.999	CT	1.041	0.32	24.30	1978	MPC01
		1.75			65.9	3.008	1.493	CT	1.504	0.30	23.50	1978	MPC01
		1.75			65.9	3.003	1.503	CT	1.552	0.36	25.20	1978	RA002
		2.50			66.0	3.017	0.999	CT	1.448	0.30	23.30	1978	MPC01
		3.00			66.0	2.500	0.754	CT	1.279	0.29	22.60	1972	84306

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN ORIENT (F)	YIELD STRENGTH (KSI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	2.5* (K(I C)/TVB)**2 (IN)	K(I C) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER
	FORM	THICK (IN)			WIDTH (IN)	THICK (IN)	DESIGN	A						
T851	P	2.03	R. T.	66.0	3.020	1.500	CT	1.510	0.50	30.20	30.20		1978	MPC01
		3.00		66.0	2.500	0.795	CT	1.270	0.35	24.60	24.60		1972	B4306
		2.75		66.2	3.026	1.247	CT	1.543	0.34	24.70	24.70		1978	MPC01
		1.50		66.2	3.003	1.502	CT	1.584	0.43	27.70	27.70		1978	RA002
		2.50		66.2	2.985	1.440	CT	1.552	0.40	26.60	26.60		1978	MPC01
		1.50		66.2	2.988	1.441	CT	1.524	0.38	26.20	26.20		1978	MPC01
		2.50		66.2	1.997	0.999	CT	1.035	0.27	22.10	22.10		1979	RA001
		1.50		66.2	2.977	1.499	CT	1.543	0.34	24.90	24.90		1978	RA001
		2.00		66.4	3.018	1.499	CT	1.539	0.38	26.10	26.10		1978	MPC01
		1.55		66.4	1.998	0.997	CT	1.019	0.32	24.90	24.90		1978	MPC01
		2.50		66.5	3.029	1.496	CT	1.484	0.30	23.70	23.70		1978	MPC01
		1.12		66.5	2.981	1.500	CT	1.550	0.28	23.00	23.00		1978	MPC01
		1.81		66.5	3.002	1.478	CT	1.544	0.36	25.90	25.90		1980	RA001
		1.25		66.5	2.004	1.000	CT	1.022	0.36	25.40	25.40		1978	MPC01
		1.73		66.6	2.990	1.497	CT	1.495	0.34	24.70	24.70		1978	MPC01
		1.50		66.6	1.998	0.999	CT	1.014	0.28	23.30	23.30		1978	MPC01
		1.57		66.7	3.000	1.497	CT	1.050	0.25	21.90	21.90		1978	MPC01
		2.50		66.7	2.999	1.499	CT	1.517	0.32	24.10	24.10		1978	RA002
		1.50		66.8	3.000	1.497	CT	1.522	0.31	23.60	23.60		1980	RA001
		1.50		66.9	1.983	0.999	CT	1.033	0.42	27.40	27.40		1978	MPC01
		1.50		67.1	2.998	1.496	CT	1.051	0.25	22.00	22.00		1978	MPC01
		1.57		67.2	3.000	1.500	CT	1.485	0.29	23.00	23.00		1978	RA001
		1.57		67.2	3.000	1.500	CT	1.590	0.35	25.10	25.10		1972	B4368
		1.57		67.2	3.000	1.500	CT	1.560	0.32	24.00	24.00		1972	B4368
		1.73		67.2	3.000	1.500	CT	1.560	0.32	24.00	24.00		1972	B4368
		1.50		67.2	3.000	1.500	CT	1.590	0.35	25.30	25.30		1972	B4368
		1.55		67.2	3.002	1.498	CT	1.550	0.32	24.10	24.10		1978	RA002
		1.75		67.3	3.001	1.497	CT	1.524	0.29	23.20	23.20		1980	RA001
		2.52		67.6	2.000	1.000	CT	1.563	0.28	22.90	22.90		1979	RA001
		2.52		67.6	2.000	1.000	CT	1.518	0.31	23.79	23.79		1980	RA001
	1.50		67.8	3.009	1.499	CT	0.960	0.29	23.10	23.10		1972	B4368	
	1.37		68.4	3.002	1.400	CT	1.595	0.28	22.60	22.60		1972	B4368	
	1.62		69.6	2.978	1.376	CT	1.591	0.27	22.60	22.60		1978	MPC01	
				3.000	1.451	CT	1.489	0.25	22.90	22.90		1978	MPC01	
				3.000	1.498	CT	1.524	0.29	24.10	24.10	25.1/	2.3	1980	RA001
T851	P	3.50	81	63.7	3.000	1.498	CT	1.618	0.37	24.40	24.40		1973	86213
				63.7	3.000	1.498	CT	1.601	0.39	25.00	25.00	24.7/	0.4	1973

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM										K(IIC)	2124	K(IIC)	CRACK LENGTH (IN)	2.5* (K(IIC)/TYS)**2 (IN)	K(IIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER	
	---PRODUCT--- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	---SPECIMEN---		DESIGN THICK (IN)	W	A										B
						WIDTH (IN)	THICK (IN)													
T851	P	2.50	250	T-L	57.3	2.000	1.000	CT	---	---	---	0.56	27.10	1974	88742					
		2.50			57.3	2.000	1.000	CT	---	---	---	0.56	26.90	1974	88742					
		2.50			57.3	2.000	1.000	CT	---	---	---	0.59	27.70	1974	88742					
T851	P	2.50	R.T.	S-T	62.3	2.000	1.000	CT	---	---	---	0.40	24.70	1974	88742					
		2.50			62.3	2.000	1.000	CT	---	---	---	0.43	24.80	1974	88742					
		2.50			62.3	2.000	1.000	CT	---	---	---	0.44	26.00	1974	88742					
T851	P	2.50	250	S-T	55.9	2.000	1.000	CT	---	---	---	0.53	26.20	1974	88742					
		2.50			55.9	2.000	1.000	CT	---	---	---	0.46	24.60	1974	88742					
T851	P	1.50	R.T.	S-L	---	1.001	0.501	CT	0.501	---	---	---	19.50	1978	RA001					
		1.50			---	1.001	0.502	CT	0.503	---	---	---	20.20	1978	RA001					
		1.50			---	1.002	0.498	CT	0.489	---	---	---	18.40	1980	RA001					
		1.50			---	1.001	0.497	CT	0.525	---	---	---	20.50	1980	RA001					
		1.50			---	1.001	0.497	CT	0.518	---	---	---	20.40	1980	RA001					
		6.00			52.7	2.015	0.999	CT	1.068	---	---	0.48	23.40	1978	MPC01					
		6.00			52.7	1.994	1.000	CT	0.977	---	---	0.44	22.30	1978	MPC01					
		6.00			52.8	1.998	0.997	CT	1.029	---	---	0.51	23.90	1978	RA001					
		6.00			53.0	2.000	1.000	CT	0.940	---	---	0.42	22.20	1978	MPC01					
		5.50			53.2	1.985	0.999	CT	1.052	---	---	0.44	22.90	1978	MPC01					
		5.50			53.9	2.014	1.000	CT	0.987	---	---	0.52	24.80	1978	MPC01					
		5.50			54.0	2.002	0.999	CT	1.021	---	---	0.50	24.60	1978	MPC01					
		5.00			54.1	1.992	1.002	CT	0.996	---	---	0.48	24.30	1978	MPC01					
		6.00			54.2	1.996	1.000	CT	0.998	---	---	0.34	20.10	1978	MPC01					
		4.90			54.2	3.000	1.498	CT	1.480	---	---	0.43	22.70	1978	RA002					
		5.00			54.2	2.004	0.998	CT	1.002	---	---	0.34	20.50	1978	MPC01					
		6.00			54.3	1.006	0.496	CT	0.533	---	---	0.34	20.50	1978	MPC01					
		5.50			54.3	2.019	0.999	CT	0.969	---	---	0.38	21.60	1978	MPC01					
		5.12			54.4	1.991	0.999	CT	1.075	---	---	0.40	21.80	1978	MPC01					
		4.90			54.4	1.988	1.000	CT	0.954	---	---	0.32	19.60	1978	MPC01					
	6.00			54.6	3.000	1.500	CT	1.500	---	---	0.44	23.10	1978	MPC01						
	5.75			54.6	1.999	0.996	CT	0.986	---	---	0.36	20.90	1980	RA001						
	5.00			54.6	1.992	0.996	CT	0.996	---	---	0.38	21.80	1978	MPC01						
	5.50			54.7	1.984	0.999	CT	0.972	---	---	0.42	22.80	1978	MPC01						
	6.00			54.8	3.000	1.500	CT	1.530	---	---	0.50	24.50	1972	84368						
	6.00			54.8	3.000	1.500	CT	1.530	---	---	0.50	24.90	1972	84368						
	5.00			54.9	2.984	1.199	CT	1.552	---	---	0.38	21.90	1978	MPC01						
	4.50			55.2	2.004	0.996	CT	0.973	---	---	0.43	23.10	1980	RA001						

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN		DESIGN	CRACK LENGTH (IN)	2.5* K(KIC)/TYS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	K(KIC) STAN DEV	DATE	REFER
	FORM	THICK (IN)		THICK (IN)	THICK (IN)							
T851	P	5.50	55.2	1.988	1.000	CT	1.014	0.52	25.90		1978	MPC01
		5.00	55.2	2.974	1.500	CT	1.576	0.46	23.90		1978	MPC01
		5.12	55.2	2.015	0.998	CT	1.048	0.46	24.20		1978	MPC01
		5.50	55.2	2.000	0.998	CT	0.978	0.39	20.90		1980	RA001
		6.00	55.4	1.993	1.000	CT	1.056	0.48	24.60		1978	MPC01
		6.00	55.7	1.996	1.000	CT	1.018	0.48	24.80		1978	MPC01
		5.50	55.8	2.021	0.998	CT	0.970	0.40	22.40		1978	MPC01
		5.00	55.8	1.998	1.000	CT	0.988	0.36	21.29		1979	RA001
		4.90	55.8	3.005	1.500	CT	1.517	0.36	21.40		1978	RA002
		5.00	55.9	2.972	1.498	CT	1.486	0.36	21.60		1978	MPC01
		5.00	56.0	2.000	0.999	CT	0.977	0.36	21.29		1980	RA001
		6.00	56.0	2.002	0.996	CT	1.002	0.44	23.60		1980	RA001
		5.25	56.0	2.975	1.500	CT	1.547	0.38	22.00		1978	MPC01
		5.50	56.0	2.010	1.000	CT	1.005	0.28	19.20		1978	MPC01
		5.50	56.1	1.990	1.000	CT	1.035	0.32	20.30		1978	MPC01
		6.00	56.2	1.982	1.000	CT	1.011	0.48	24.80		1978	MPC01
		4.25	56.2	2.000	0.929	CT	0.957	0.33	20.60		1980	RA001
		5.00	56.3	2.980	1.498	CT	1.490	0.38	22.10		1978	MPC01
		5.50	56.3	2.010	1.000	CT	1.009	0.30	19.70		1978	MPC01
		4.50	56.3	2.000	1.001	CT	0.992	0.38	22.00		1978	RA002
		4.90	56.4	1.996	0.998	CT	1.018	0.32	20.60		1978	MPC01
		5.25	56.4	2.016	1.000	CT	1.008	0.28	19.30		1980	RA001
		4.00	56.5	2.002	0.997	CT	1.026	0.38	22.29		1978	MPC01
		5.50	56.6	2.008	1.000	CT	1.004	0.46	24.40		1978	MPC01
		5.50	56.6	1.994	0.999	CT	1.017	0.38	22.50		1978	MPC01
		6.00	56.6	1.998	0.998	CT	0.998	0.43	23.50		1978	RA001
		4.62	56.6	3.033	1.499	CT	1.456	0.46	24.70		1978	MPC01
		5.50	56.6	2.000	1.000	CT	1.020	0.36	22.00		1978	MPC01
		2.50	56.6	1.999	1.000	CT	1.052	0.39	21.29		1978	RA002
		4.90	56.7	3.000	1.499	CT	1.596	0.43	23.60		1978	RA002
		4.00	56.7	2.000	0.998	CT	0.980	0.36	21.60		1980	RA001
		5.50	56.7	1.992	0.997	CT	0.956	0.32	20.70		1978	MPC01
		4.50	56.7	1.998	0.998	CT	1.009	0.37	22.10		1979	RA001
		5.50	56.8	2.012	1.000	CT	1.006	0.36	21.80		1978	MPC01
		4.62	56.8	1.996	0.999	CT	0.996	0.30	20.20		1978	MPC01
		5.50	56.8	2.008	1.000	CT	1.004	0.28	19.70		1978	MPC01
		4.90	56.8	3.000	1.499	CT	1.526	0.37	22.00		1978	RA002
		5.00	56.9	2.988	1.499	CT	1.494	0.38	22.60		1978	MPC01
		5.00	56.9	1.997	0.998	CT	1.005	0.39	21.40		1979	RA001

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (NSI)	SPECIMEN		W	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(1C)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KBSQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)		THICK (IN)	THICK (IN)										
T851	P	4.00	56.9	2.002	0.999	CT	0.984	0.35	21.50	1980	RA001				
		5.50	57.0	2.002	1.000	CT	1.001	0.28	19.70	1978	MPC01				
		5.50	57.0	1.994	1.000	CT	1.017	0.24	17.70	1978	MPC01				
		5.50	57.0	2.014	1.000	CT	1.007	0.25	18.30	1978	MPC01				
		4.50	57.0	1.994	1.000	CT	0.997	0.25	18.50	1978	MPC01				
		5.50	57.1	2.017	0.999	CT	1.069	0.42	23.50	1978	MPC01				
		5.50	57.1	2.000	1.000	CT	1.000	0.27	19.00	1978	MPC01				
		4.75	57.1	2.000	0.998	CT	0.980	0.59	22.79	1980	RA001				
		5.50	57.1	1.998	1.000	CT	0.999	0.30	20.50	1978	MPC01				
		2.20	57.1	1.503	0.748	CT	0.774	0.27	19.00	1980	RA001				
		5.50	57.1	2.008	1.000	CT	1.004	0.34	21.60	1978	MPC01				
		5.50	57.1	2.010	1.000	CT	1.005	0.34	21.60	1978	MPC01				
		5.00	57.1	2.012	1.000	CT	1.006	0.40	23.20	1978	MPC01				
		5.50	57.3	2.010	1.000	CT	1.005	0.28	19.70	1978	MPC01				
		4.50	57.3	3.000	1.500	CT	1.540	0.51	25.80	1972	84368				
		4.50	57.3	3.000	1.500	CT	1.540	0.47	24.70	1972	84368				
		4.00	57.3	1.998	0.999	CT	1.022	0.34	21.20	1978	RA001				
		5.50	57.5	3.000	1.500	CT	1.470	0.43	23.20	1972	84368				
		5.50	57.5	3.000	1.500	CT	1.500	0.42	23.60	1972	84368				
		5.50	57.5	1.998	1.000	CT	0.999	0.28	20.00	1978	MPC01				
		4.00	57.5	2.000	0.999	CT	0.984	0.33	21.20	1980	RA001				
		5.50	57.6	1.988	1.000	CT	1.014	0.42	23.70	1978	MPC01				
		4.31	57.6	1.992	0.999	CT	1.036	0.34	21.60	1978	MPC01				
		5.50	57.6	2.006	0.999	CT	1.003	0.32	20.80	1978	MPC01				
		4.00	57.6	3.001	1.500	CT	1.564	0.34	21.50	1978	RA001				
		5.50	57.6	1.986	1.000	CT	0.993	0.34	21.60	1978	MPC01				
		5.00	57.6	1.998	0.997	CT	0.997	0.36	22.10	1978	RA001				
	5.00	57.6	1.992	1.000	CT	1.016	0.40	23.20	1978	MPC01					
	4.55	57.6	2.004	0.999	CT	0.985	0.34	21.50	1980	RA001					
	5.50	57.7	2.022	1.000	CT	1.011	0.30	20.20	1978	MPC01					
	4.50	57.7	2.017	0.999	CT	1.049	0.38	22.70	1978	MPC01					
	3.00	57.8	2.002	1.001	CT	1.001	0.30	20.70	1978	MPC01					
	4.00	57.8	2.987	1.498	CT	1.643	0.40	23.50	1978	MPC01					
	5.50	57.8	2.000	1.000	CT	1.000	0.36	22.00	1978	MPC01					
	3.50	57.8	1.993	1.001	CT	1.096	0.32	21.00	1978	MPC01					
	5.00	57.8	2.000	1.001	CT	1.009	0.29	19.70	1978	RA002					
	5.50	57.8	1.984	1.000	CT	1.012	0.42	24.20	1978	MPC01					
	5.50	57.9	1.992	1.000	CT	0.996	0.28	20.00	1978	MPC01					

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEMP (F)	R. T.	S-L	SPECIMEN		WIDTH (IN)	THICK (IN)	DEBION (IN)	CRACK LENGTH (IN)	K(1C) (KSI*SQRT IN)	K(1C) MEAN DEV (KSI*SQRT IN)	STAN DEV	DATE	REFER			
	FORM	THICK (IN)						M	B										A	2.5*	K(1C)
1851	P	5.50	57.9					1.000	CT	2.008	1.000	1.004	0.25	19.00			1978	MPC01			
		3.62	58.0					0.998	CT	2.006	0.998	1.003	0.32	21.30			1978	MPC01			
		5.50	58.0					1.501	CT	3.008	1.501	1.504	0.38	23.10			1978	MPC01			
		4.00	58.0					1.001	CT	2.004	1.001	1.002	0.36	22.30			1978	MPC01			
		5.00	58.1					1.000	CT	2.010	1.000	1.005	0.38	23.00			1978	MPC01			
		2.50	58.1					1.986	CT	1.986	1.000	1.013	0.40	23.80			1978	MPC01			
		5.50	58.1					2.016	CT	2.016	1.000	1.008	0.38	22.70			1978	MPC01			
		5.50	58.1					2.002	CT	2.002	1.000	1.001	0.40	23.40			1978	MPC01			
		5.50	58.1					3.024	CT	3.024	1.500	1.512	0.42	23.90			1978	MPC01			
		2.50	58.1					2.008	CT	2.008	0.996	1.004	0.30	20.50			1978	MPC01			
		5.00	58.1					1.992	CT	1.992	1.001	1.016	0.34	21.50			1978	MPC01			
		4.90	58.1					2.000	CT	2.000	1.001	1.010	0.34	21.60			1978	RA002			
		2.50	58.1					2.018	CT	2.018	1.000	1.029	0.42	24.30			1978	MPC01			
		3.00	58.2					2.004	CT	2.004	0.997	1.030	0.31	20.70			1980	RA001			
		5.50	58.2					2.010	CT	2.010	1.000	1.025	0.30	20.50			1978	MPC01			
		2.70	58.2					1.988	CT	1.988	1.002	0.974	0.42	24.10			1978	MPC01			
		5.00	58.2					2.006	CT	2.006	0.999	1.023	0.40	23.40			1978	MPC01			
		5.00	58.2					1.984	CT	1.984	0.999	1.012	0.38	22.90			1978	MPC01			
		5.50	58.2					3.008	CT	3.008	1.500	1.504	0.40	23.70			1978	MPC01			
		5.50	58.3					1.996	CT	1.996	1.000	0.998	0.30	20.60			1978	MPC01			
		5.25	58.3					3.020	CT	3.020	1.500	1.510	0.44	24.80			1978	MPC01			
		3.12	58.3					2.016	CT	2.016	1.001	0.988	0.36	22.40			1978	MPC01			
		5.50	58.3					1.998	CT	1.998	1.000	0.999	0.30	20.50			1978	MPC01			
		5.50	58.3					1.998	CT	1.998	1.000	0.999	0.30	20.60			1978	MPC01			
		5.50	58.3					2.014	CT	2.014	1.000	0.999	0.30	20.60			1978	MPC01			
		5.50	58.3					2.014	CT	2.014	1.000	1.007	0.40	23.40			1978	MPC01			
		5.50	58.3					2.000	CT	2.000	0.998	1.007	0.28	20.00			1978	MPC01			
		5.50	58.3					2.016	CT	2.016	0.990	0.983	0.32	20.90			1980	RA001			
		5.50	58.3					2.004	CT	2.004	0.999	1.002	0.30	20.90			1978	MPC01			
		4.00	58.4					1.999	CT	1.999	1.000	1.002	0.50	26.60			1978	MPC01			
		1.81	58.4					1.502	CT	1.502	0.748	0.766	0.28	19.79			1979	RA001			
		4.50	58.4					2.978	CT	2.978	1.500	1.489	0.24	18.50			1978	MPC01			
		5.50	58.4					2.020	CT	2.020	0.997	1.010	0.46	25.20			1978	MPC01			
		5.00	58.4					3.010	CT	3.010	1.500	1.565	0.28	20.40			1978	MPC01			
		2.50	58.5					1.996	CT	1.996	1.000	0.998	0.30	20.70			1978	MPC01			
		5.50	58.5					2.018	CT	2.018	1.000	1.009	0.34	22.00			1978	MPC01			
		4.25	58.5					1.987	CT	1.987	0.999	1.033	0.40	23.50			1978	MPC01			
		4.25	58.5					1.996	CT	1.996	1.000	0.998	0.27	19.60			1978	MPC01			
		5.00	58.6					1.983	CT	1.983	0.999	1.031	0.36	22.30			1978	MPC01			

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN THICK (IN)	TEST TEMP (F)	ORIENT	S-L	SPECIMEN		CRACK LENGTH (IN)	2.5* K(1C) (IN)	K(1C)/TYS)**2	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
	M							B								
	FORM	THICK (IN)						WIDTH (IN)	DESIGN							
T851	P	5.50	58.6	2.006	0.999	CT	1.003	0.30	20.80	1978	MPC01					
		3.50	58.6	2.008	1.000	CT	1.024	0.34	21.80	1978	MPC01					
		5.00	58.6	1.988	1.000	CT	1.014	0.42	24.50	1978	MPC01					
		5.50	58.6	2.008	1.000	CT	1.004	0.40	23.90	1978	MPC01					
		4.50	58.6	2.996	1.500	CT	1.498	0.48	26.00	1978	MPC01					
		5.00	58.6	1.994	0.999	CT	1.017	0.38	23.00	1978	MPC01					
		4.00	58.6	1.996	0.999	CT	0.998	0.32	21.10	1978	MPC01					
		5.50	58.6	1.998	1.000	CT	0.999	0.38	22.90	1978	MPC01					
		5.50	58.6	2.018	0.999	CT	1.009	0.48	26.00	1978	MPC01					
		5.50	58.7	2.010	1.000	CT	1.005	0.27	19.50	1978	MPC01					
		3.54	58.7	1.998	0.997	CT	0.999	0.32	21.70	1978	MPC01					
		5.50	58.8	2.016	1.000	CT	1.008	0.48	26.00	1978	MPC01					
		5.50	58.8	2.004	0.998	CT	1.002	0.38	23.20	1978	MPC01					
		5.50	58.8	2.000	1.000	CT	1.000	0.36	22.50	1978	MPC01					
		4.25	58.8	2.002	1.000	CT	1.001	0.34	21.90	1978	MPC01					
		5.50	58.8	1.996	1.000	CT	1.078	0.30	20.70	1978	MPC01					
		5.50	58.8	2.014	1.000	CT	1.007	0.34	22.30	1978	MPC01					
		4.50	58.8	2.999	1.500	CT	1.487	0.34	21.79	1978	RA002					
		5.50	58.8	2.006	0.998	CT	1.003	0.40	23.80	1978	MPC01					
		5.50	58.9	2.020	1.000	CT	1.010	0.28	20.50	1978	MPC01					
		4.00	58.9	1.984	1.001	CT	1.012	0.38	23.10	1978	MPC01					
		4.50	58.9	2.992	1.500	CT	1.496	0.44	25.00	1978	MPC01					
		4.25	59.0	1.996	1.000	CT	1.018	0.36	23.00	1978	MPC01					
		5.00	59.1	1.988	1.000	CT	1.014	0.34	22.00	1978	MPC01					
		5.00	59.1	1.986	1.000	CT	1.013	0.34	22.00	1978	MPC01					
		5.50	59.1	2.000	1.000	CT	1.400	0.30	20.79	1978	GD003					
		5.50	59.1	2.002	1.000	CT	1.001	0.36	22.80	1978	MPC01					
		5.50	59.1	2.000	1.000	CT	1.400	0.34	22.00	1978	GD003					
		5.00	59.1	1.996	1.000	CT	1.000	0.28	20.20	1978	MPC01					
		5.00	59.1	1.984	0.999	CT	1.012	0.32	21.60	1978	MPC01					
		5.00	59.1	2.010	1.000	CT	1.005	0.36	23.00	1978	MPC01					
		2.75	59.1	2.000	1.000	CT	1.013	0.29	20.29	1978	RA002					
		5.50	59.1	1.980	1.000	CT	0.990	0.46	25.90	1978	MPC01					
		5.50	59.1	2.000	1.000	CT	1.400	0.32	21.40	1978	GD003					
		5.50	59.1	2.008	1.000	CT	1.004	0.42	24.50	1978	MPC01					
		3.12	59.2	1.998	0.999	CT	1.004	0.40	23.70	1978	RA001					
		5.00	59.2	1.986	1.001	CT	1.013	0.34	22.90	1978	MPC01					
		3.12	59.2	2.018	0.996	CT	0.989	0.32	21.80	1978	MPC01					
		4.50	59.2	2.998	1.500	CT	1.499	0.48	26.30	1978	MPC01					

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	2.5* K(KIC)/TVB)**2 (IN)	K(KIC) MEAN DEV (KSI*SQRT IN)	K(KIC) STAN DEV (IN)	DATE	REFER
	FORM	THICK (IN)			THICK (IN)	WIDTH (IN)	THICK (IN)	DESIGN (IN)						
T851	P	4.50	R. T.	59.2	3.018	1.500	CT	1.509	0.48	26.10			1978	MPC01
		5.00		59.2	2.024	1.001	CT	1.012	0.36	22.90			1978	MPC01
		5.00		59.3	1.992	1.001	CT	1.016	0.40	23.90			1978	MPC01
		5.00		59.3	1.998	1.000	CT	0.999	0.42	24.90			1978	MPC01
		4.00		59.3	2.000	1.000	CT	0.980	0.38	23.40			1972	84368
		4.25		59.3	1.990	0.987	CT	1.019	0.42	24.40			1978	MPC01
		5.00		59.3	1.978	1.001	CT	1.009	0.42	24.70			1978	MPC01
		4.00		59.3	2.000	1.000	CT	0.980	0.44	24.80			1972	84368
		5.50		59.3	2.008	1.000	CT	1.024	0.50	26.90			1978	MPC01
		4.25		59.3	2.024	1.000	CT	1.012	0.30	21.20			1978	MPC01
		5.00		59.3	2.014	1.001	CT	1.007	0.40	24.00			1978	MPC01
		5.50		59.4	2.018	1.000	CT	1.007	0.34	22.20			1978	MPC01
		4.25		59.4	1.998	1.000	CT	0.999	0.40	23.90			1978	MPC01
		4.25		59.4	1.994	1.000	CT	1.017	0.38	23.70			1978	MPC01
		3.12		59.4	2.000	0.972	CT	1.000	0.30	21.20			1978	MPC01
		2.50		59.4	2.000	1.001	CT	1.018	0.35	22.50			1978	RA002
		4.25		59.4	1.994	1.001	CT	0.997	0.50	27.20			1978	MPC01
		1.75		59.4	1.002	0.479	CT	0.511	0.30	20.70			1980	RA001
		4.25		59.5	1.990	1.000	CT	1.015	0.48	26.30			1978	MPC01
		5.00		59.5	2.006	1.000	CT	1.003	0.36	22.70			1978	MPC01
		3.00		59.5	2.000	0.999	CT	1.000	0.30	21.00			1978	MPC01
		5.25		59.5	3.012	1.500	CT	1.506	0.42	24.50			1978	MPC01
		4.31		59.6	2.000	1.000	CT	0.970	0.42	24.50			1972	84368
		5.50		59.6	1.977	1.000	CT	1.008	0.40	24.30			1978	MPC01
		5.50		59.6	1.986	1.000	CT	1.013	0.32	21.80			1978	MPC01
		5.50		59.6	2.010	1.000	CT	1.005	0.34	22.50			1978	MPC01
		4.31		59.6	2.000	1.000	CT	0.950	0.41	24.10			1972	84368
		3.00		59.6	1.997	0.978	CT	0.999	0.26	19.50			1978	RA001
		4.25		59.7	2.014	1.002	CT	1.007	0.44	25.30			1978	MPC01
		3.50		59.7	2.004	0.995	CT	0.999	0.27	19.70			1980	RA001
	2.00		59.7	1.500	0.749	CT	0.756	0.38	23.59			1978	MPC01	
	5.50		59.8	2.012	1.000	CT	1.006	0.34	22.50			1978	MPC01	
	3.50		59.8	1.998	0.998	CT	1.001	0.32	21.70			1979	RA001	
	3.25		59.8	1.989	0.999	CT	1.054	0.30	21.20			1978	MPC01	
	5.50		59.8	1.987	1.000	CT	1.033	0.28	20.50			1978	MPC01	
	4.50		59.8	3.000	1.500	CT	1.530	0.36	22.70			1972	84368	
	4.50		59.8	3.000	1.500	CT	1.520	0.35	22.50			1972	84368	
	3.54		59.8	2.014	1.000	CT	1.007	0.34	22.30			1978	MPC01	
	5.00		59.8	2.010	1.000	CT	1.005	0.36	23.10			1978	MPC01	

TABLE 7.8.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)			THICK (IN)	THICK (IN)								
	M	B			A									
T851	P	4.25	R. T.	59.9	1.994	1.000	CT	1.017	0.27	20.30			1978	MPC01
		2.00		59.9	1.902	0.751	CT	0.751	0.22	18.40			1978	MPC01
		2.50		59.9	1.498	0.744	CT	0.760	0.26	19.60			1980	RA001
		3.00		59.9	2.006	1.001	CT	1.003	0.27	19.80			1978	MPC01
		3.50		59.9	2.000	1.000	CT	0.990	0.27	19.80			1972	84368
		3.50		59.9	2.000	1.000	CT	0.990	0.32	21.40			1972	84368
		4.50		59.9	2.998	1.500	CT	1.499	0.48	26.50			1978	MPC01
		5.50		60.0	1.998	1.000	CT	0.999	0.28	20.40			1978	MPC01
		2.90		60.0	1.988	0.998	CT	0.974	0.30	21.00			1978	MPC01
		3.00		60.0	2.003	0.995	CT	1.004	0.39	23.70			1980	RA001
		5.00		60.1	1.996	0.999	CT	0.998	0.44	25.70			1978	MPC01
		4.00		60.1	2.002	0.998	CT	0.998	0.35	22.60			1980	RA001
		4.50		60.1	3.008	1.501	CT	1.504	0.38	23.80			1978	MPC01
		3.54		60.1	2.004	0.998	CT	1.002	0.42	24.80			1978	MPC01
		3.12		60.1	1.997	0.998	CT	1.019	0.36	23.40			1978	MPC01
		2.50		60.2	2.010	0.996	CT	1.005	0.32	22.00			1978	MPC01
		4.50		60.2	3.029	1.500	CT	1.484	0.42	24.70			1978	MPC01
		4.25		60.2	1.986	1.000	CT	1.013	0.32	21.70			1978	MPC01
		5.50		60.2	2.016	1.000	CT	1.008	0.24	19.00			1978	MPC01
		4.00		60.2	3.000	1.500	CT	1.540	0.27	20.00			1972	84368
		2.50		60.4	1.999	0.999	CT	1.096	0.27	19.90			1978	RA002
		4.00		60.5	2.014	0.999	CT	1.007	0.34	22.60			1978	MPC01
		5.00		60.6	1.996	0.999	CT	1.018	0.34	23.00			1978	MPC01
		5.50		60.6	2.004	0.999	CT	1.002	0.30	21.70			1978	MPC01
		3.00		60.6	2.004	0.999	CT	1.022	0.36	23.10			1978	MPC01
		3.00		60.6	1.999	1.000	CT	0.963	0.29	20.70			1978	RA002
		3.00		60.6	2.004	0.996	CT	0.998	0.29	20.90			1980	RA001
		3.00		60.6	1.999	0.998	CT	0.991	0.27	20.00			1980	RA001
		4.00		60.6	3.026	1.501	CT	1.513	0.38	23.70			1978	MPC01
		4.00		60.6	2.992	1.500	CT	1.526	0.36	23.70			1978	MPC01
		4.25		60.7	2.016	1.000	CT	1.008	0.28	20.30			1978	MPC01
		3.12		60.7	1.998	0.997	CT	1.039	0.30	20.30			1978	MPC01
		2.50		60.7	0.986	0.502	CT	0.498	0.22	9.10			1978	RA002
		3.00		60.7	1.992	0.999	CT	1.019	0.24	19.20			1978	MPC01
		3.00		60.8	1.997	0.998	CT	1.020	0.30	21.40			1978	RA001
		5.00		60.8	2.016	1.000	CT	1.008	0.25	20.00			1978	MPC01
		3.62		60.8	1.996	0.999	CT	0.979	0.25	19.50			1980	RA001
		3.00		60.9	2.006	1.001	CT	1.023	0.27	20.20			1978	MPC01

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEMP (F)	THICK (IN)	W	SPECIMEN		DESIGN THICK (IN)	CRACK LENGTH (IN)	2 S* (K(IC)/TYS)**2 (IN)	K(IC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)						A	B							
T851	P	3.62	60.9	S-L	R.T.	5-L	3.014	1.499	CT	1.567	0.28	20.80		1978	MPC01	
		4.25	60.9				1.984	1.000	CT	1.012	0.30	21.70		1978	MPC01	
		3.50	60.9				2.016	0.997	CT	1.008	0.34	22.70		1978	MPC01	
		3.00	60.9				2.000	1.000	CT	0.991	0.31	21.70		1978	RA002	
		5.50	60.9				2.004	1.000	CT	1.002	0.27	20.30		1978	MPC01	
		2.50	60.9				2.006	0.998	CT	1.003	0.28	21.30		1978	MPC01	
		4.00	60.9				1.997	0.999	CT	1.002	0.36	23.20		1978	RA001	
		2.00	61.0				1.498	0.751	CT	0.756	0.29	21.10		1978	RA002	
		5.50	61.1				2.014	1.003	CT	1.007	0.32	22.30		1978	MPC01	
		4.25	61.1				1.996	1.001	CT	0.998	0.36	23.90		1978	MPC01	
		3.50	61.1				1.998	0.999	CT	1.022	0.33	22.20		1978	RA001	
		1.62	61.2				0.986	0.503	CT	0.480	0.24	19.10		1978	RA002	
		3.00	61.2				1.996	0.998	CT	1.018	0.25	19.70		1978	MPC01	
		3.00	61.2				2.000	0.999	CT	0.980	0.28	20.79		1980	RA001	
		3.75	61.3				3.016	1.499	CT	1.538	0.30	21.90		1978	MPC01	
		2.50	61.3				1.499	0.745	CT	0.750	0.24	19.29		1980	RA001	
		5.50	61.4				1.986	1.003	CT	1.013	0.34	23.00		1978	MPC01	
		3.50	61.4				2.000	1.000	CT	0.990	0.43	25.40		1972	84368	
		2.50	61.4				2.000	1.000	CT	1.100	0.27	20.80		1978	MPC01	
		2.00	61.4				0.997	0.498	CT	0.504	0.25	19.60		1978	RA001	
		3.50	61.4				2.000	1.000	CT	0.990	0.41	24.70		1972	84368	
		4.90	61.4				3.000	1.500	CT	1.585	0.36	23.40		1978	RA002	
		4.00	61.5				3.000	1.500	CT	1.530	0.30	21.70		1978	MPC01	
		1.75	61.6				0.998	0.503	CT	0.520	0.21	17.90		1980	RA001	
		3.00	61.6				2.000	1.001	CT	1.012	0.22	18.50		1978	RA002	
		4.90	61.6				3.000	1.499	CT	1.592	0.35	23.10		1978	RA002	
		5.50	61.6				1.986	1.000	CT	1.013	0.38	24.30		1978	MPC01	
		2.35	61.7				1.502	0.750	CT	0.763	0.33	22.50		1980	RA001	
		1.73	61.7				1.004	0.497	CT	0.542	0.21	18.40		1978	MPC01	
		3.12	61.7				2.002	0.998	CT	0.996	0.29	21.29		1980	RA001	
		3.00	61.8				1.999	0.994	CT	1.000	0.23	19.10		1980	RA001	
		3.00	61.8				1.980	0.999	CT	1.010	0.27	20.80		1978	MPC01	
		2.00	61.9				1.498	0.749	CT	0.794	0.25	20.10		1978	MPC01	
		4.75	62.0				2.004	1.000	CT	1.002	0.29	20.40		1978	MPC01	
		2.50	62.0				1.984	0.998	CT	1.012	0.24	19.70		1978	MPC01	
		2.25	62.0				0.998	0.499	CT	0.539	0.24	19.80		1978	MPC01	
		3.00	62.0				2.010	1.001	CT	1.009	0.27	20.80		1978	MPC01	
		3.00	62.0				1.995	0.998	CT	0.960	0.30	21.60		1980	RA001	
		3.00	62.0				1.997	0.999	CT	1.007	0.24	19.40		1979	RA001	

TABLE 7.8.2.1 (Con't)

CONDITION	---PRODUCT---		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	---SPECIMEN---		CRACK LENGTH (IN)	K(I,C)		DATE	REFER	
	FORM	THICK (IN)			THICK (IN)	DESIGN		2.5*	(K(I,C)/TYS)**2			(K(I,C) MEAN DEV (KSI*SQRT IN))
			(F)		W	B	A	(IN)	(IN)			
T851	P	2.50	R. T.	62.0	1.499	0.744	CT	0.741	0.23	18.90	1980	RA001
		5.50		62.1	2.001	1.000	CT	1.006	0.30	22.00	1978	MPC01
		2.50		62.1	2.000	1.000	CT	1.020	0.40	25.30	1978	MPC01
		2.50		62.1	2.000	1.000	CT	0.940	0.31	21.80	1972	84368
		3.00		62.1	1.997	0.998	CT	1.022	0.29	21.90	1979	RA001
		2.50		62.1	2.000	1.000	CT	0.960	0.34	22.90	1972	84368
		2.50		62.1	1.998	1.000	CT	1.019	0.38	24.90	1978	MPC01
		3.00		62.1	2.003	0.998	CT	0.995	0.29	21.90	1980	RA001
		1.50		62.2	0.996	0.501	CT	0.508	0.34	23.10	1978	MPC01
		2.00		62.2	1.489	0.746	CT	0.774	0.25	20.20	1978	MPC01
		2.75		62.2	1.988	1.001	CT	1.014	0.28	21.90	1978	MPC01
		2.75		62.2	2.004	0.996	CT	1.004	0.31	22.20	1980	RA001
		1.75		62.2	1.000	0.500	CT	0.503	0.21	18.10	1978	RA002
		1.50		62.2	0.998	0.501	CT	0.509	0.34	23.10	1978	MPC01
		2.50		62.2	1.502	0.750	CT	0.768	0.30	21.60	1980	RA001
		4.75		62.4	1.994	1.001	CT	1.017	0.30	22.40	1978	MPC01
		2.75		62.4	1.499	0.746	CT	0.755	0.33	22.79	1980	RA001
		2.50		62.5	2.000	1.001	CT	1.020	0.24	19.60	1978	MPC01
		5.50		62.6	2.000	1.000	CT	1.000	0.28	21.60	1978	MPC01
		1.75		62.6	0.979	0.500	CT	0.475	0.31	22.29	1978	RA002
		2.50		62.6	2.000	1.001	CT	0.979	0.28	21.10	1978	RA002
		5.50		62.6	2.000	1.000	CT	1.000	0.30	22.10	1978	MPC01
		2.00		62.6	2.020	0.998	CT	0.990	0.30	22.10	1978	MPC01
		2.04		62.7	1.512	0.751	CT	0.771	0.22	19.20	1978	MPC01
		2.50		62.7	1.500	0.750	CT	0.730	0.21	18.10	1972	84368
		2.04		62.7	1.500	0.750	CT	0.730	0.20	17.60	1972	84368
		2.50		62.7	1.500	0.751	CT	0.776	0.22	18.70	1980	RA001
		2.03		62.8	1.471	0.750	CT	0.738	0.28	21.00	1980	RA001
		1.50		62.8	1.008	0.498	CT	0.534	0.32	23.00	1978	MPC01
		2.25		62.8	1.510	0.749	CT	0.785	0.21	18.90	1978	MPC01
		2.00		62.8	1.493	0.748	CT	0.791	0.29	20.60	1978	MPC01
		2.00		62.9	1.489	0.749	CT	0.774	0.28	21.50	1978	MPC01
		3.00		62.9	2.015	1.001	CT	1.048	0.30	22.60	1978	MPC01
		2.03		62.9	1.496	0.750	CT	0.763	0.36	24.10	1978	MPC01
		2.50		62.9	2.000	1.000	CT	0.930	0.28	21.20	1972	84368
		2.50		62.9	2.000	1.000	CT	0.930	0.28	21.10	1972	84368
		1.81		63.0	1.006	0.496	CT	0.533	0.18	17.10	1978	MPC01
		1.50		63.0	1.002	0.500	CT	0.521	0.32	22.80	1978	MPC01

TABLE 7.8.2.1 (Con't)

CONDITION	P	--PRODUCT--		TEST SPECIMEN ORIENT	YIELD STRENGTH (KBI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	2.5% K(IIC) (IN)	K(IIC) MEAN (KBI*SQRT IN)	K(IIC) STAN DEV (KBI*SQRT IN)	DATE	REFER
		FORM	THICK (IN)			WIDTH (IN)	THICK (IN)	DESIGN							
		M	N			A	B								
1851		2.00	R.T.	S-L	63.0	1.002	0.495	CT	0.531	0.22	19.20	1978	MPC01		
		1.50			63.0	1.000	0.500	CT	0.510	0.27	21.00	1978	MPC01		
		1.57			63.0	1.000	0.500	CT	0.490	0.29	21.60	1978	84368		
		2.40			63.2	1.500	0.747	CT	0.749	0.27	20.79	1980	RA001		
		3.00			63.3	1.994	1.001	CT	1.017	0.30	22.40	1978	MPC01		
		1.81			63.4	0.998	0.499	CT	0.509	0.16	17.00	1978	MPC01		
		2.75			63.4	2.000	0.998	CT	0.983	0.32	22.79	1980	RA001		
		2.50			63.5	2.000	1.000	CT	0.960	0.27	21.80	1972	84368		
		2.50			63.5	2.000	1.000	CT	0.970	0.31	22.20	1972	84368		
		1.55			63.5	0.999	0.501	CT	0.469	0.22	19.00	1980	RA001		
		1.55			63.6	1.000	0.498	CT	0.540	0.28	22.10	1978	MPC01		
		1.75			63.6	1.010	0.499	CT	0.525	0.18	17.50	1978	MPC01		
		2.50			63.7	2.000	0.998	CT	0.960	0.27	21.20	1978	MPC01		
		2.35			63.9	0.998	0.498	CT	0.537	0.18	17.40	1978	MPC01		
		1.50			63.9	0.999	0.501	CT	0.487	0.27	21.00	1980	RA001		
		2.00			64.1	1.502	0.751	CT	0.766	0.28	22.00	1978	MPC01		
		3.12			64.2	2.006	0.999	CT	1.003	0.24	20.50	1978	MPC01		
		2.75			64.3	1.499	0.752	CT	0.767	0.29	21.90	1978	RA002		
		1.55			64.3	1.000	0.497	CT	0.540	0.28	21.30	1972	84368		
		1.57			64.4	1.000	0.500	CT	0.490	0.27	21.30	1972	84368		
		1.57			64.4	1.000	0.500	CT	0.500	0.25	20.50	1972	84368		
		2.50			64.4	2.000	0.998	CT	0.964	0.26	20.90	1978	RA002		
		2.50			64.4	1.499	0.745	CT	0.754	0.17	17.20	1980	RA001		
		2.00			64.5	1.518	0.751	CT	0.774	0.25	20.70	1978	MPC01		
		1.75			64.5	1.012	0.501	CT	0.526	0.19	18.30	1978	MPC01		
		2.00			64.6	1.499	0.751	CT	0.793	0.19	18.00	1978	RA002		
		1.75			64.8	0.979	0.502	CT	0.509	0.24	20.10	1978	RA002		
		2.50			64.8	2.002	0.998	CT	1.021	0.18	18.00	1978	MPC01		
		2.00			64.8	1.498	0.746	CT	0.782	0.22	20.00	1978	MPC01		
		2.25			64.9	1.489	0.749	CT	0.746	0.18	17.79	1980	RA001		
		2.00			64.9	1.491	0.750	CT	0.774	0.19	18.30	1978	MPC01		
		2.00			64.9	1.500	0.750	CT	0.805	0.22	20.10	1978	MPC01		
		2.00			64.9	1.500	0.750	CT	0.740	0.22	19.20	1972	84368		
		1.73			65.0	0.986	0.502	CT	0.740	0.22	19.10	1972	84368		
		1.75			65.2	0.998	0.500	CT	0.467	0.26	21.10	1978	RA002		
		1.75			65.2	1.000	0.500	CT	0.495	0.18	17.50	1980	RA001		
		1.75			65.3	1.010	0.505	CT	0.500	0.17	17.29	1978	RA001		
		1.75			65.3	1.000	0.500	CT	0.505	0.18	18.10	1978	MPC01		
		1.75			65.3	1.000	0.500	CT	0.460	0.19	18.20	1972	84368		

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEMP (F)	PRODUCT-- THICK (IN)	SPECIMEN			DESIGN	CRACK LENGTH (IN)	K(IC) 2.5* (KSI*SQRT IN)	K(IC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER	
	2124						K(IC)										
	M	B					A										
T851	P	1.75	R.T.	65.3	S-L	1.000	0.500	CT	0.490	0.22	19.50			1972	84368		
		1.57		65.4		1.000	0.500	CT	0.470	0.21	18.80			1972	84368		
		2.25		65.5		1.489	0.749	CT	0.774	0.22	19.90			1978	MPC01		
		2.25		65.6		2.016	0.999	CT	1.028	0.21	19.60			1978	MPC01		
		2.50		65.7		1.504	0.749	CT	0.782	0.25	21.50			1978	MPC01		
		2.50		65.7		1.991	1.001	CT	1.055	0.24	21.00			1978	MPC01		
		1.55		65.8		0.976	0.500	CT	0.528	0.18	18.00			1978	MPC01		
		2.50		66.1		1.500	0.749	CT	0.760	0.16	16.79			1979	RA001		
		2.52		66.3		2.000	1.000	CT	0.970	0.24	20.60			1972	84368		
		2.52		66.3		2.000	1.000	CT	0.950	0.20	18.80			1972	84368		
		1.62		66.6		1.001	0.498	CT	0.475	0.16	16.90			1980	RA001		
		1.73		67.2		1.001	0.498	CT	0.519	0.21	19.90			1978	RA002		
		1.75		67.4		1.000	0.520	CT	0.520	0.15	17.50			1978	MPC01		
		1.55		68.1		1.001	0.499	CT	0.517	0.19	18.79	21.7/	2.1		1979	RA001	
		T851	P	3.50	82	59.8	S-L	2.000	0.998	CT	0.986	0.33	22.40			1973	86213
3.50				59.8		2.000	0.998	CT	0.941	0.33	21.80	22.1/	0.4		1973	86213	
T851	P	3.00	84	61.3	S-L	2.000	0.999	CT	0.931	0.38	23.90			1973	86213		
		3.00		61.6		2.000	0.999	CT	0.954	0.41	25.00	24.5/	0.8		1973	86213	
T851 (SP)	P	6.00	R.T.	57.1	L-T	3.000	1.500	CT	1.522	0.65	29.10			1973	86213		
		6.00		57.1		3.000	1.500	CT	1.549	0.68	29.70			1973	86213		
		4.50		59.8		3.000	1.501	CT	1.532	0.77	33.10			1973	86213		
		4.50		59.8		3.000	1.500	CT	1.509	0.71	31.90			1973	86213		
		2.04		65.4		1.900	0.752	CT	0.752	0.26	21.10			1973	86213		
		2.04		65.4		1.900	0.752	CT	0.738	0.27	21.50			1973	86213		
		4.00		65.5		3.000	1.500	CT	1.578	0.31	23.00			1973	86213		
		4.00		65.5		2.990	1.501	CT	1.562	0.30	22.50			1973	86213		
		2.00		66.2		3.000	1.501	CT	1.555	0.52	30.50			1973	86213		
		2.00		66.2		3.000	1.502	CT	1.564	0.53	30.40	27.2/	4.7		1973	86213	
		T851 (SP)	P	6.00	R.T.	55.0	T-L	3.000	1.500	CT	1.563	0.46	23.70			1973	86213
				6.00		55.0		3.000	1.500	CT	1.576	0.48	24.10			1973	86213
4.50				58.5		3.000	1.500	CT	1.567	0.51	26.50			1973	86213		
2.04				65.2		1.900	0.732	CT	0.741	0.22	19.50			1973	86213		
2.04		65.2		1.500	0.751	CT	0.729	0.22	19.40			1973	86213				

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	SPECIMEN THICKNESS (IN)		CRACK LENGTH (IN)	2.5* K(KIC)/TYS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	WIDTH (IN)				A	B						
T851 (SP)	P	2.00	65.4	R.T.	T-L	3.000	1.502	CT	1.542	24.40	23.1/	2.7	1973 86213
		2.00	65.4			3.000	1.500	CT	1.541	24.10			1973 86213
T851 (SP)	P	6.00	54.8	R.T.	S-L	3.000	1.500	CT	1.526	24.50			1973 86213
		6.00	54.8			3.000	1.500	CT	1.539	24.80			1973 86213
		4.50	57.3			3.000	1.502	CT	1.543	25.80			1973 86213
		4.50	57.3			3.000	1.500	CT	1.542	24.90			1973 86213
		4.00	60.2			3.000	1.502	CT	1.560	19.90			1973 86213
		4.00	60.2			3.000	1.501	CT	1.540	20.00			1973 86213
		2.04	62.7			1.500	0.752	CT	0.729	17.60			1973 86213
		2.04	62.7			1.500	0.751	CT	0.726	18.10			1973 86213
		2.00	64.9			1.500	0.750	CT	0.739	19.20			1973 86213
		2.00	64.9			1.490	0.750	CT	0.737	19.10	21.4/	3.2	
T851 (417)	P	4.50	76.4	- 320	L-T	3.000	1.500	CT	1.478	31.90			1973 86213
		1.75	80.9			3.000	1.500	CT	1.641	33.80	32.7/	1.1	1973 86213
T851 (417)	P	4.50	67.6	- 112	L-T	3.000	1.501	CT	1.474	27.90			1973 86213
		1.75	73.2			3.000	1.499	CT	1.642	29.60	28.8/	1.2	1973 86213
T851 (417)	P	4.00	60.6	R.T.	L-T	2.000	1.000	NB	0.925	34.30			1973 86213
		5.50	61.1			3.000	1.501	CT	1.495	28.80			1973 86213
		5.50	61.1			3.000	1.501	CT	1.496	28.10			1973 86213
		4.00	62.5			2.000	1.000	NB	0.932	31.90			1973 86213
		4.00	62.5			2.000	1.000	NB	0.941	32.70			1973 86213
		4.50	63.1			3.000	1.501	CT	1.479	26.60			1973 86213
		4.50	63.4			3.000	1.500	CT	1.536	27.70			1973 86213
		4.50	63.4			3.000	1.502	CT	1.518	26.70			1973 86213
		3.50	63.9			3.000	1.501	CT	1.523	31.50			1973 86213
		3.50	63.9			3.000	1.501	CT	1.510	31.60			1973 86213
		1.57	64.2			3.000	1.501	CT	1.589	27.40			1973 86213
		1.57	64.2			3.000	1.501	CT	1.581	28.00			1973 86213
		1.57	65.2			3.000	1.500	CT	1.526	35.20			1973 86213
		3.00	65.4			3.000	1.501	CT	1.477	34.20			1973 86213
		3.00	65.4			3.000	1.412	CT	1.546	28.70			1973 86213
		3.00	65.4			1.000	0.499	CT	0.517	24.80			1973 86213
3.00	65.4			2.000	0.999	CT	1.014	26.80			1973 86213		

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM										K (IC)	K (IC) STAN K (IC) MEAN DEV (KSI*SQRT IN)	DATE	REFER
	---PRODUCT---		YIELD STRENGTH (KSI)	---SPECIMEN---		CRACK LENGTH (IN)	2.5* (K(IC)/TYS)**2 (IN)	K (IC)		K (IC) STAN K (IC) MEAN DEV (KSI*SQRT IN)				
	FORM	THICK TEMP (F)		THICK ORIENT	THICK DESIGN			WIDTH (IN)	THICK (IN)					
T851 (417)	P	3.00	R. T.	L-T	3.000	0.999	CT	1.536	0.45	27.80	1973	86213		
		3.00			3.000	1.412	CT	1.532	0.48	28.90	1973	86213		
		3.00			1.000	0.498	CT	0.515	0.36	25.00	1973	86213		
		3.00			2.000	0.998	CT	1.019	0.40	26.90	1973	86213		
		3.00			3.000	0.998	CT	1.530	0.48	28.90	1973	86213		
		1.75			3.000	1.501	CT	1.572	0.46	28.60	1973	86213		
		1.75			3.000	1.502	CT	1.583	0.45	28.30	1973	86213		
		1.57			3.000	1.502	CT	1.560	0.37	26.00	1973	86213		
		1.57			3.000	1.502	CT	1.559	0.37	26.90	1973	86213		
		1.75			3.000	1.499	CT	1.631	0.46	29.10	28.9/	2.8	1973	86213
	T851 (417)	P	3.50	81	L-T	3.990	1.500	CT	1.537	0.45	27.90	1973	86213	
			2.00			3.990	1.995	CT	2.087	0.62	32.90	1973	86213	
					3.990	1.995	CT	2.032	0.43	28.10	29.5/	2.6	1973	86213
T891 (417)	P	3.75	82	L-T	2.000	0.999	CT	1.015	0.51	27.80	1973	86213		
		3.38			2.000	1.000	CT	0.955	0.47	26.70	1973	86213		
		3.38			2.000	1.000	CT	0.950	0.51	27.80	1973	86213		
		3.15			2.000	0.998	CT	0.995	0.49	28.00	1973	86213		
		3.75			2.000	0.998	CT	0.997	0.44	27.00	1973	86213		
		3.75			2.000	1.001	CT	1.000	0.45	27.10	1973	86213		
		3.75			2.000	1.000	CT	1.012	0.43	26.90	1973	86213		
		3.15			2.000	0.999	CT	0.980	0.43	27.00	1973	86213		
		3.38			2.000	1.000	CT	0.957	0.41	26.40	1973	86213		
		3.38			2.000	0.998	CT	0.965	0.41	26.30	1973	86213		
		2.50			1.990	1.002	CT	1.018	0.43	27.10	1973	86213		
		2.50			1.990	1.001	CT	1.006	0.44	27.30	1973	86213		
		2.50			4.000	1.997	CT	2.103	0.77	36.40	1973	86213		
		2.50			4.000	1.997	CT	2.097	0.78	36.70	1973	86213		
		3.15			2.000	0.999	CT	0.960	0.37	26.10	1973	86213		
		3.15			2.000	0.998	CT	0.959	0.41	26.70	1973	86213		
		2.50			3.990	1.998	CT	2.181	0.51	29.80	1973	86213		
		2.50			3.990	2.000	CT	2.159	0.65	33.70	1973	86213		
	2.75			2.000	1.000	CT	0.958	0.36	25.90	1973	86213			
	2.75			2.000	0.998	CT	0.953	0.34	24.90	1973	86213			
	2.75			2.000	0.998	CT	0.945	0.34	24.80	1973	86213			
	2.75			2.000	0.999	CT	0.958	0.34	25.30	1973	86213			
	2.52			2.000	0.999	CT	0.963	0.35	26.00	1973	86213			

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	SPECIMEN			CRACK LENGTH (IN)	K(1C) 2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER	
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)	DESIGN							A
T851 (417)	P	2.52	69.7	82	L-T	2.000	0.998	CT	0.939	0.33	25.20		1973	86213	
		2.52	69.7			2.000	1.001	CT	0.960	0.33	25.50	28.0/	3.5	1973	86213
T851 (417)	P	1.75	78.1	- 320	T-L	3.000	1.500	CT	1.648	0.35	29.10			1973	86213
T851 (417)	P	4.50	66.0	- 112	T-L	3.000	1.498	CT	1.567	0.33	24.10			1973	86213
		1.75	70.7			3.000	1.500	CT	1.623	0.30	24.60	24.4/	0.4	1973	86213
T851 (417)	P	5.50	59.3	R. T.	T-L	3.000	1.501	CT	1.514	0.34	21.80			1973	86213
		5.50	59.3			3.000	1.501	CT	1.540	0.35	22.30			1973	86213
		4.00	59.4			2.000	1.001	NB	0.938	0.49	26.40			1973	86213
		4.50	61.4			3.000	1.501	CT	1.566	0.36	23.30			1973	86213
		4.50	61.4			3.000	1.501	CT	1.523	0.34	22.50			1973	86213
		4.50	61.5			3.000	1.500	CT	1.482	0.29	21.10			1973	86213
		4.00	62.6			2.000	0.998	NB	0.918	0.40	24.90			1973	86213
		3.50	62.7			3.000	1.501	CT	1.550	0.44	26.40			1973	86213
		3.50	62.7			3.000	1.501	CT	1.546	0.46	26.80			1973	86213
		3.00	64.4			3.000	0.998	CT	1.520	0.31	22.70			1973	86213
		3.00	64.4			1.000	0.499	CT	0.525	0.27	21.10			1973	86213
		3.00	64.4			2.000	0.999	CT	0.996	0.26	20.70			1973	86213
		3.00	64.4			3.000	1.412	CT	1.553	0.31	22.70			1973	86213
		3.00	64.8			3.000	0.498	CT	1.526	0.31	22.20			1973	86213
		3.00	64.8			3.000	1.412	CT	1.551	0.29	22.20			1973	86213
		3.00	64.8			1.000	0.498	CT	0.516	0.28	21.80			1973	86213
		3.00	64.8			3.000	0.998	CT	1.541	0.31	22.70			1973	86213
		3.00	64.8			3.000	0.497	CT	1.512	0.30	22.50			1973	86213
		3.00	64.8			2.000	0.998	CT	1.034	0.28	21.50			1973	86213
		1.57	65.2			3.000	1.501	CT	1.522	0.51	29.40			1973	86213
	1.75	65.2			3.000	1.501	CT	1.541	0.54	30.30			1973	86213	
	1.75	65.7			3.000	1.500	CT	1.577	0.33	23.90			1973	86213	
	1.75	65.7			3.000	1.502	CT	1.565	0.33	24.00			1973	86213	
	1.75	66.0			3.000	1.500	CT	1.643	0.34	24.50			1973	86213	
	1.57	67.2			3.000	1.502	CT	1.561	0.32	24.00			1973	86213	
	1.57	67.2			3.000	1.501	CT	1.591	0.35	25.30			1973	86213	
	1.57	67.2			3.000	1.502	CT	1.565	0.32	24.00			1973	86213	
	1.57	67.2			3.000	1.501	CT	1.591	0.35	25.10	23.8/	2.4	1973	86213	
T851 (417)	P	3.50	64.2	81	T-L	3.000	1.498	CT	1.520	0.33	23.30			1973	86213
		3.50	64.2			3.000	1.499	CT	1.545	0.32	22.80			1973	86213

TABLE 7.8.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	THICK (IN)	SPECIMEN		CRACK LENGTH (IN)	CRACK 2.9* (K(IC)/TYS)**2 (IN)	K(IC) MEAN (KSI*SQRT IN)	K(IC) STAN DEV	DATE	REFER
	FORM	THICK (IN)					WIDTH (IN)	THICK (IN)						
T851 (417)	P	2.00	65.3	T-L	81	2.00	4.000	2.000	CT	2.159	30.90	3.8	1973	86213
		2.00	66.7			1.999	4.000	1.999	CT	2.142	24.30		1973	86213
T851 (417)	P	3.75	59.2	T-L	82	2.000	2.000	0.999	CT	1.014	24.20		1973	86213
		3.38	61.0			0.998	2.000	0.998	CT	0.958	28.40		1973	86213
		3.38	61.0			0.999	2.000	0.974	CT	0.974	27.50		1973	86213
		3.00	61.8			1.500	3.000	1.560	CT	21.10	21.10		1973	86213
		3.75	63.0			1.001	2.000	1.005	CT	0.34	23.30		1973	86213
		3.75	63.0			1.000	2.000	0.999	CT	0.34	23.20		1973	86213
		3.15	63.4			1.000	2.000	1.000	CT	0.43	26.30		1973	86213
		3.75	63.8			1.001	2.000	1.011	CT	0.34	23.50		1973	86213
		3.15	64.2			1.000	2.000	1.003	CT	0.38	24.90		1973	86213
		2.50	64.2			1.990	1.990	1.039	CT	0.42	26.30		1973	86213
		2.50	64.2			1.990	1.990	1.039	CT	0.41	26.10		1973	86213
		2.50	64.4			1.997	4.000	2.099	CT	0.35	24.00		1973	86213
		2.50	64.4			1.999	3.990	2.172	CT	0.54	29.90		1973	86213
		2.50	64.4			1.997	4.000	1.997	CT	0.54	30.00		1973	86213
		3.38	64.7			0.998	2.000	0.989	CT	0.41	26.10		1973	86213
		2.50	64.8			2.001	4.000	2.134	CT	0.46	27.70		1973	86213
		2.50	64.8			1.998	4.000	2.153	CT	0.47	28.10		1973	86213
		3.15	65.0			1.001	2.000	0.982	CT	0.37	25.00		1973	86213
		3.15	65.0			0.998	2.000	0.995	CT	0.36	24.60		1973	86213
		2.75	65.3			0.999	2.000	0.968	CT	0.35	24.30		1973	86213
		1.62	65.4			1.500	3.000	1.581	CT	0.26	21.20		1973	86213
		2.75	66.1			1.000	2.000	0.957	CT	0.34	24.40		1973	86213
		2.75	66.1			1.001	2.000	0.949	CT	0.32	23.60		1973	86213
		2.75	66.9			0.998	2.000	0.940	CT	0.27	22.10		1973	86213
		2.52	67.0			0.998	2.000	0.979	CT	0.31	23.70		1973	86213
		2.52	67.6			0.998	2.000	0.955	CT	0.28	22.60		1973	86213
		2.52	67.6			1.000	2.000	0.976	CT	0.29	23.10		1973	86213
		2.52	68.6			0.995	2.000	0.987	CT	0.29	23.40	2.4	1973	86213
T851 (417)	P	4.50	72.3	S-L	- 320	1.501	3.000	1.514	CT	1.514	22.10		1973	86213
T851 (417)	P	4.50	64.8	S-L	- 112	1.500	3.000	1.461	CT	1.461	21.30		1973	86213
T851 (417)	P	5.50	57.5	S-L	R.T.	1.499	3.000	1.500	CT	1.500	23.60		1973	86213
		4.00	57.5			1.501	3.000	1.466	CT	1.466	23.90		1973	86213
			59.3			0.997	2.000	0.981	CT	0.44	24.80		1973	86213

TABLE 7.8.2.1 (Con't)

CONDITION	P	FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		WIDTH (IN)	SPECIMEN THICK		DESIGN	CRACK LENGTH (IN)	K(1C)	2.9* (K(1C)/TVS)**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
							M	B		A									
T851 (417)	P	4.50	R.T.	S-L	59.8	3.000	1.501	CT	1.523	0.35	22.50	1973	86213						
					59.8	3.000	1.501	CT	1.534	0.36	22.70	1973	86213						
					60.0	2.000	1.000	CT	1.015	0.29	20.40	1973	86213						
					60.9	3.000	1.501	CT	1.459	0.29	20.70	1973	86213						
					62.1	2.000	0.998	CT	0.939	0.31	21.80	1973	86213						
					62.1	2.000	0.998	CT	0.963	0.34	22.90	1973	86213						
					62.9	2.000	0.998	CT	0.931	0.28	21.20	1973	86213						
					62.9	2.000	0.998	CT	0.926	0.28	21.10	1973	86213						
					63.0	1.000	0.500	CT	0.493	0.29	21.60	1973	86213						
					63.0	1.000	0.501	CT	0.500	0.28	21.00	1973	86213						
					63.1	2.000	0.998	CT	0.929	0.26	20.30	1973	86213						
					64.4	1.000	0.500	CT	0.489	0.27	21.30	1973	86213						
					64.4	1.000	0.500	CT	0.499	0.25	20.50	1973	86213						
					65.3	0.990	0.501	CT	0.459	0.19	18.20	1973	86213						
					65.4	0.990	0.500	CT	0.471	0.21	18.80	1973	86213						
					65.4	1.000	0.500	CT	0.488	0.16	16.70	1973	86213						
					T851 (417)	P	3.75	82	S-L	58.1	2.000	1.000	CT	0.976	0.37	22.30	1973	86213	
59.6	2.000	1.001	CT	0.947						0.40	23.90	1973	86213						
59.9	2.000	0.998	CT	0.987						0.27	19.80	1973	86213						
59.9	2.000	0.998	CT	0.992						0.32	21.40	1973	86213						
61.4	1.990	1.001	CT	0.985						0.40	24.70	1973	86213						
61.4	1.990	1.001	CT	0.988						0.43	25.40	1973	86213						
61.4	2.000	0.998	CT	0.962						0.48	26.90	1973	86213						
62.2	2.000	1.001	CT	0.983						0.36	23.60	1973	86213						
62.3	2.000	1.000	CT	0.938						0.34	22.90	1973	86213						
62.6	2.000	0.999	CT	0.955						0.33	22.90	1973	86213						
63.3	2.000	1.000	CT	0.935						0.28	21.30	1973	86213						
63.9	1.990	1.001	CT	0.965						0.29	21.80	1973	86213						
63.5	1.990	1.001	CT	0.974						0.31	22.20	1973	86213						
64.2	2.000	0.998	CT	0.929						0.25	20.50	1973	86213						
65.1	2.000	1.000	CT	0.963						0.29	22.00	1973	86213						
66.0	2.000	0.999	CT	0.948						0.18	17.80	1973	86213						
66.1	2.000	0.998	CT	0.947						0.21	19.30	1973	86213						
66.3	2.000	0.998	CT	0.945	0.20	18.80	1973	86213											
66.3	2.000	0.998	CT	0.974	0.24	20.60	1973	86213											
T851 (417)	P	3.75	84	S-L	62.2	2.000	0.998	CT	0.998	0.34	23.10	1973	86213						

TABLE 7.8.2.2

CONDITION	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	ALUMINUM				CRACK LENGTH GROSS STRESS				K(C)		K(C) STAN MEAN DEV (KSI*SQRT IN)	K(C) STAN MEAN DEV (KSI*SQRT IN)	DATE	REFER		
				W		B		INIT		FINAL		MAX						K(APP) MEAN DEV (KSI*SQRT IN)	K(C) MEAN DEV (KSI*SQRT IN)
				W	B	2A(O)	2A(F)	(IN)	(IN)	(KSI)	(KSI)	S(O)	S(MAX)						
1851	P	0.25	R. T.	T-L	59.8	3.000	0.249	1.220	1.780	18.80	26.80	41.41	58.04*	1973	86213				
		0.25			62.9	3.000	0.249	1.240	1.700	13.40	18.60	29.09	38.31	1973	86213				
		0.25			55.4	3.000	0.250	1.127	1.755	14.30	21.70	31.66	46.23*	1973	86213				
		0.25			55.5	3.000	0.251	1.128	1.778	14.90	21.90	31.99	47.36*	1973	86213				
		0.25			57.4	3.000	0.250	1.210	1.720	14.70	20.90	32.10	43.59*	1973	86213				
		0.25			57.4	3.000	0.250	1.320	1.790	13.00	20.30	33.30	44.24*	1973	86213				
		0.25			57.4	3.000	0.251	1.220	1.740	15.30	18.50	28.58	39.07	1973	86213				
		0.25			59.7	3.000	0.250	1.190	1.700	16.40	25.00	37.93	51.50*	1973	86213				
		0.25			59.7	3.000	0.250	1.220	1.690	16.30	22.20	34.30	45.45*	1973	86213				
		0.25			59.8	3.000	0.252	1.220	1.880	16.80	23.60	36.46	54.52*	1973	86213				
		0.25			59.8	3.000	0.250	1.230	1.700	16.00	23.40	36.37	48.20*	1973	86213				
		0.25			59.9	3.000	0.250	1.220	1.700	14.00	20.90	32.29	43.09*	1973	86213				
		0.25			59.9	3.000	0.250	1.250	1.640	13.30	17.10	26.90	33.95	1973	86213				
		0.25			59.9	3.000	0.250	1.240	1.640	13.40	18.50	28.93	36.73	1973	86213				
		0.25			61.1	3.000	0.250	1.240	1.800	17.30	27.10	45.91*	63.82*	1973	86213				
		0.25			61.1	3.000	0.250	1.240	1.770	17.70	26.80	41.91	57.67*	1973	86213				
		0.25			61.1	3.000	0.250	1.240	1.710	18.80	26.60	41.60	55.13*	1973	86213				
		0.25			62.9	3.000	0.250	1.240	1.600	13.30	19.90	31.12	38.57	1973	86213				
		0.25			62.9	3.000	0.250	1.200	1.650	14.00	21.20	32.36	42.35	1973	86213				

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

ALUM.
ALLOY

2124

CONDITION/HT: T851
 FORM: 5.00" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-S

SPECIMEN THK: .352"
 SPECIMEN WIDTH: 4.952"
 K_c(Ksi√in): 102.0
 REFERENCE: G0011

CONDITION/HT: T851
 FORM: 5.00" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-S

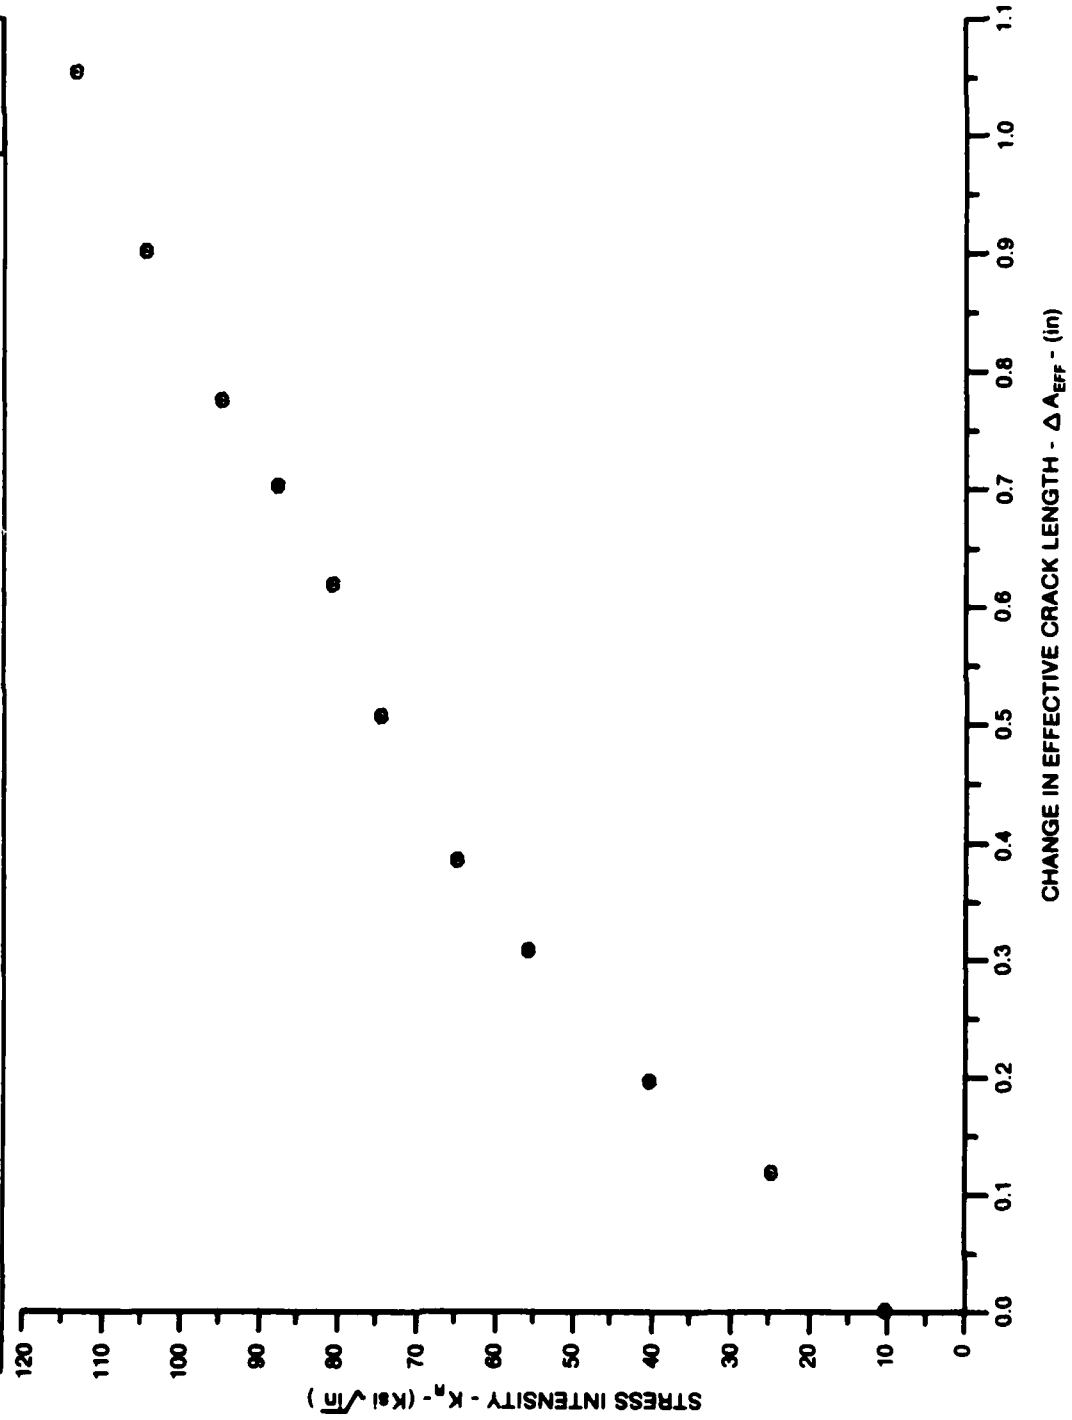


Figure 7.8.2.3

ALUM.
ALLOY

2124

SPECIMEN THK: .355"
 SPECIMEN WIDTH: 4.9160"
 K_{IC} (KSI \sqrt{in}): 75.0
 REFERENCE: GD011

CONDITION/HT: T851
 FORM: 5.00" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-S

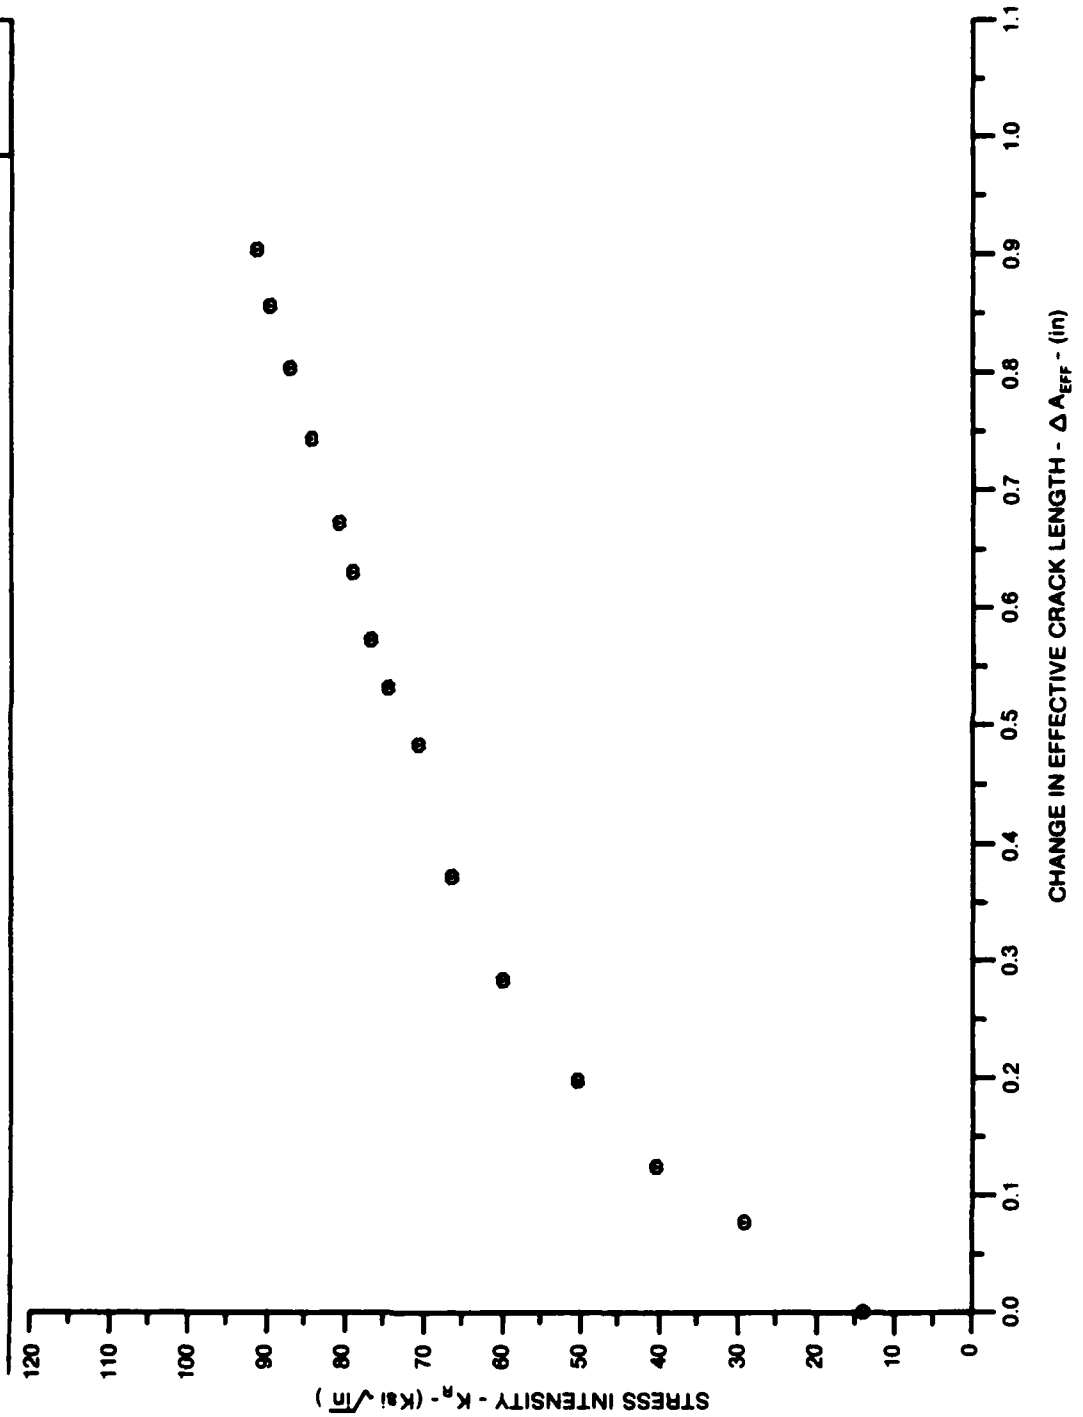


Figure 7.8.2.4

ALUM.
ALLOY

2124

SPECIMEN THK: .188"
SPECIMEN WIDTH: 6.007"
K_c (KSI√in): 82.2
REFERENCE: G0011

CONDITION: T651
FORM: 5.00" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: L-T

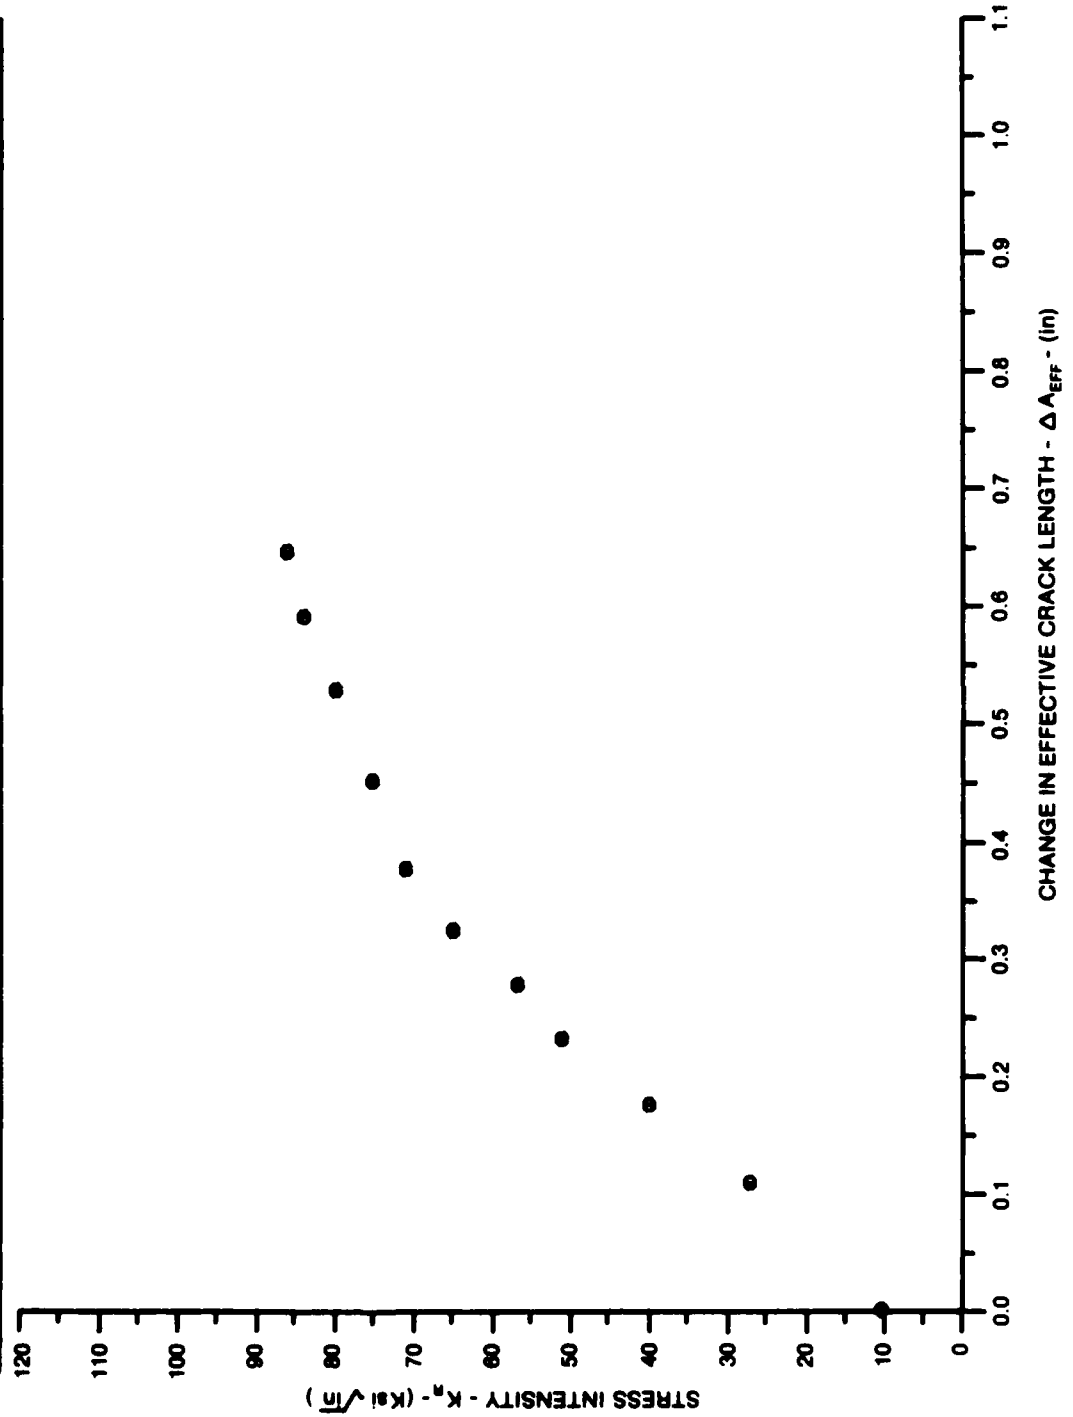


Figure 7.8.2.5

ALUM. ALLOY
2124

SPECIMEN THK: .195"
 SPECIMEN WIDTH: 8.010"
 K_I (Ksi√in): 73.2
 REFERENCE: GD011

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

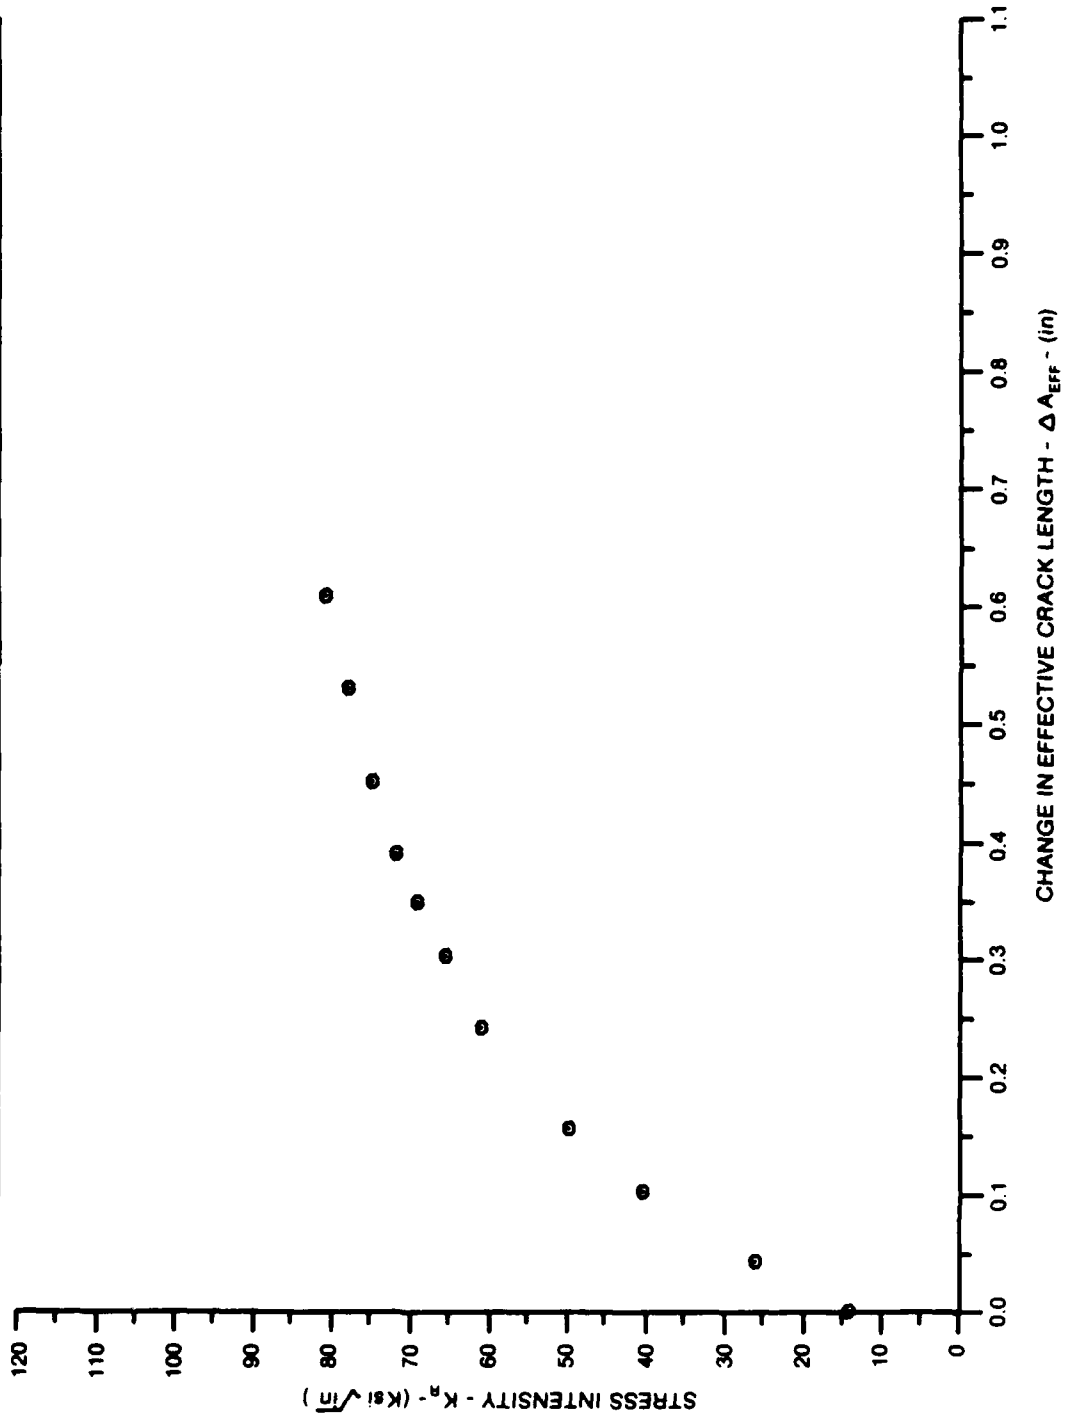


Figure 7.8.2.6

ALUM. ALLOY
2124

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 SPECIMEN THK: .193"
 SPECIMEN WIDTH: 6.885"
 K_c (Ksi√in): 98.9
 REFERENCE: G0811

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

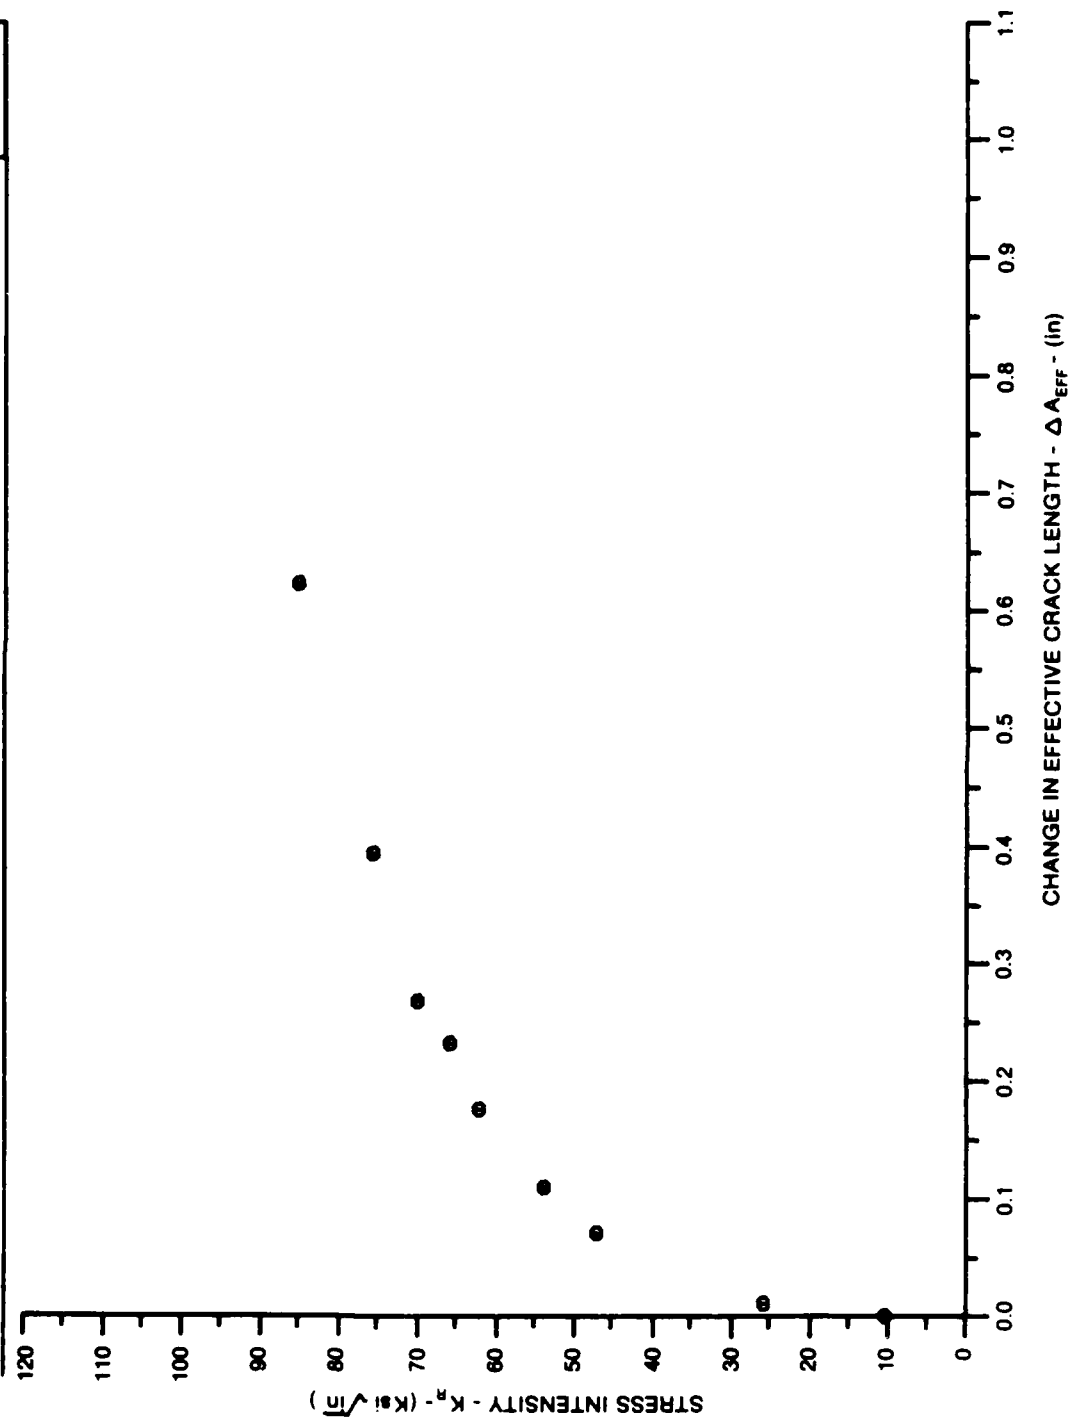


Figure 7.8.2.7

ALUM.
ALLOY

2124

SPECIMEN THK: .406"
 SPECIMEN WIDTH: 6.003"
 K_{IC} (Ksi-√in): 70.5
 REFERENCE: GDB11

CONDITION/HT: T851
 FORM: 5.00" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

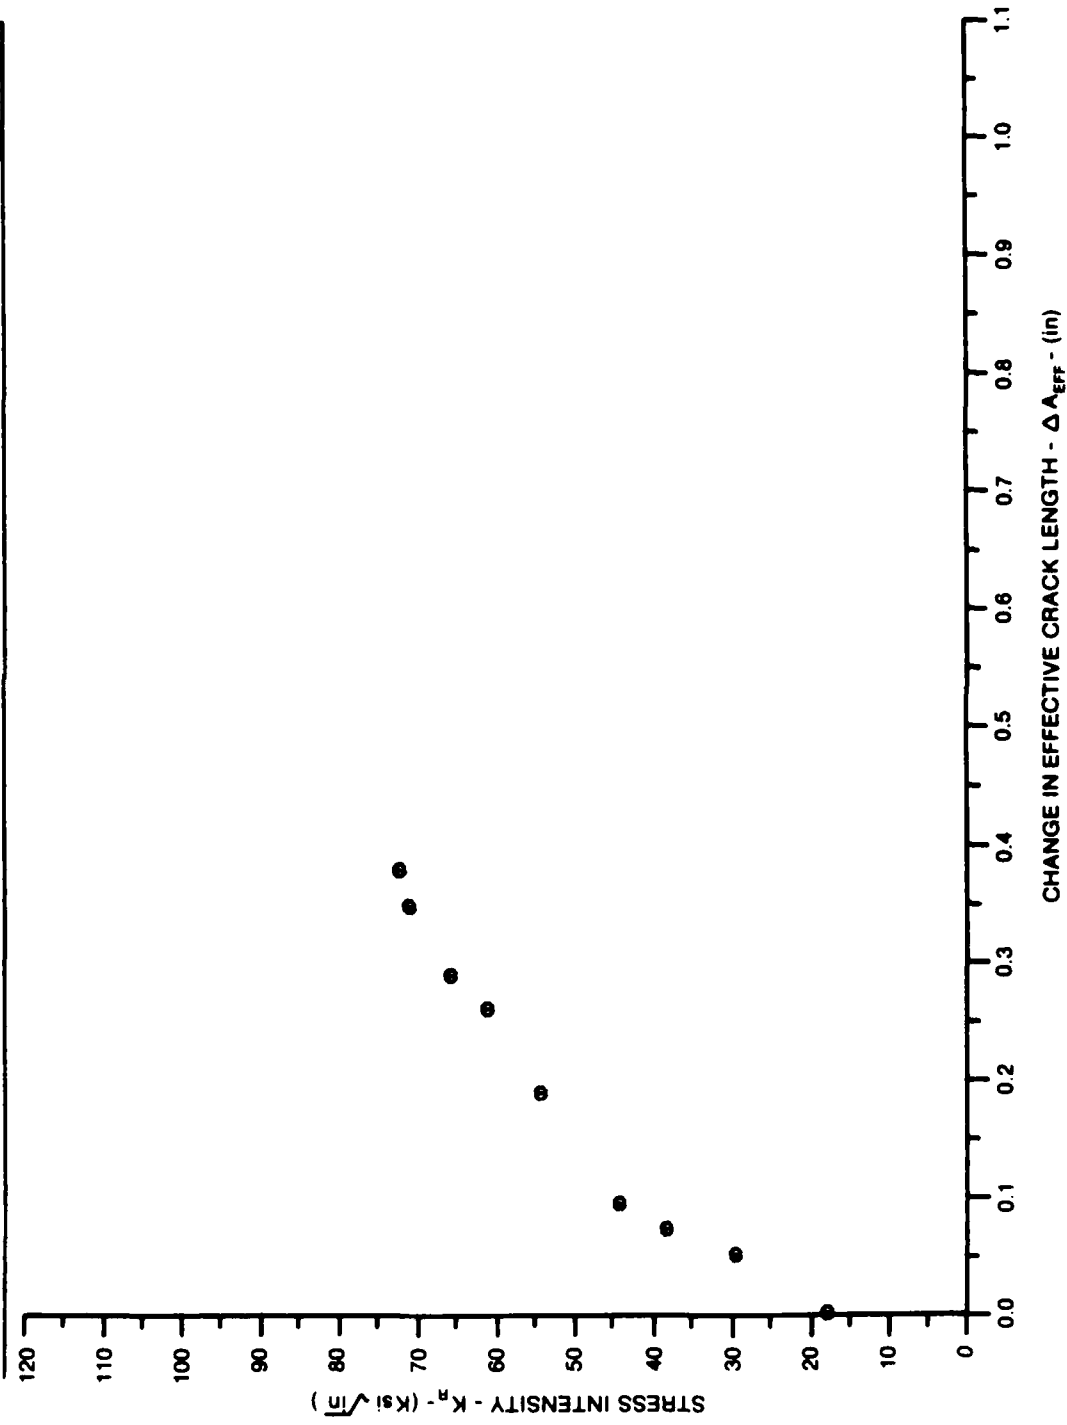


Figure 7.8.2.8

ALUM.
ALLOY

2124

SPECIMEN THK: .402"
 SPECIMEN WIDTH: 6.825"
 K_{IC} (KSI√in): 76.0
 REFERENCE: GD011

CONDITION: T651
 FORM: 5.58" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

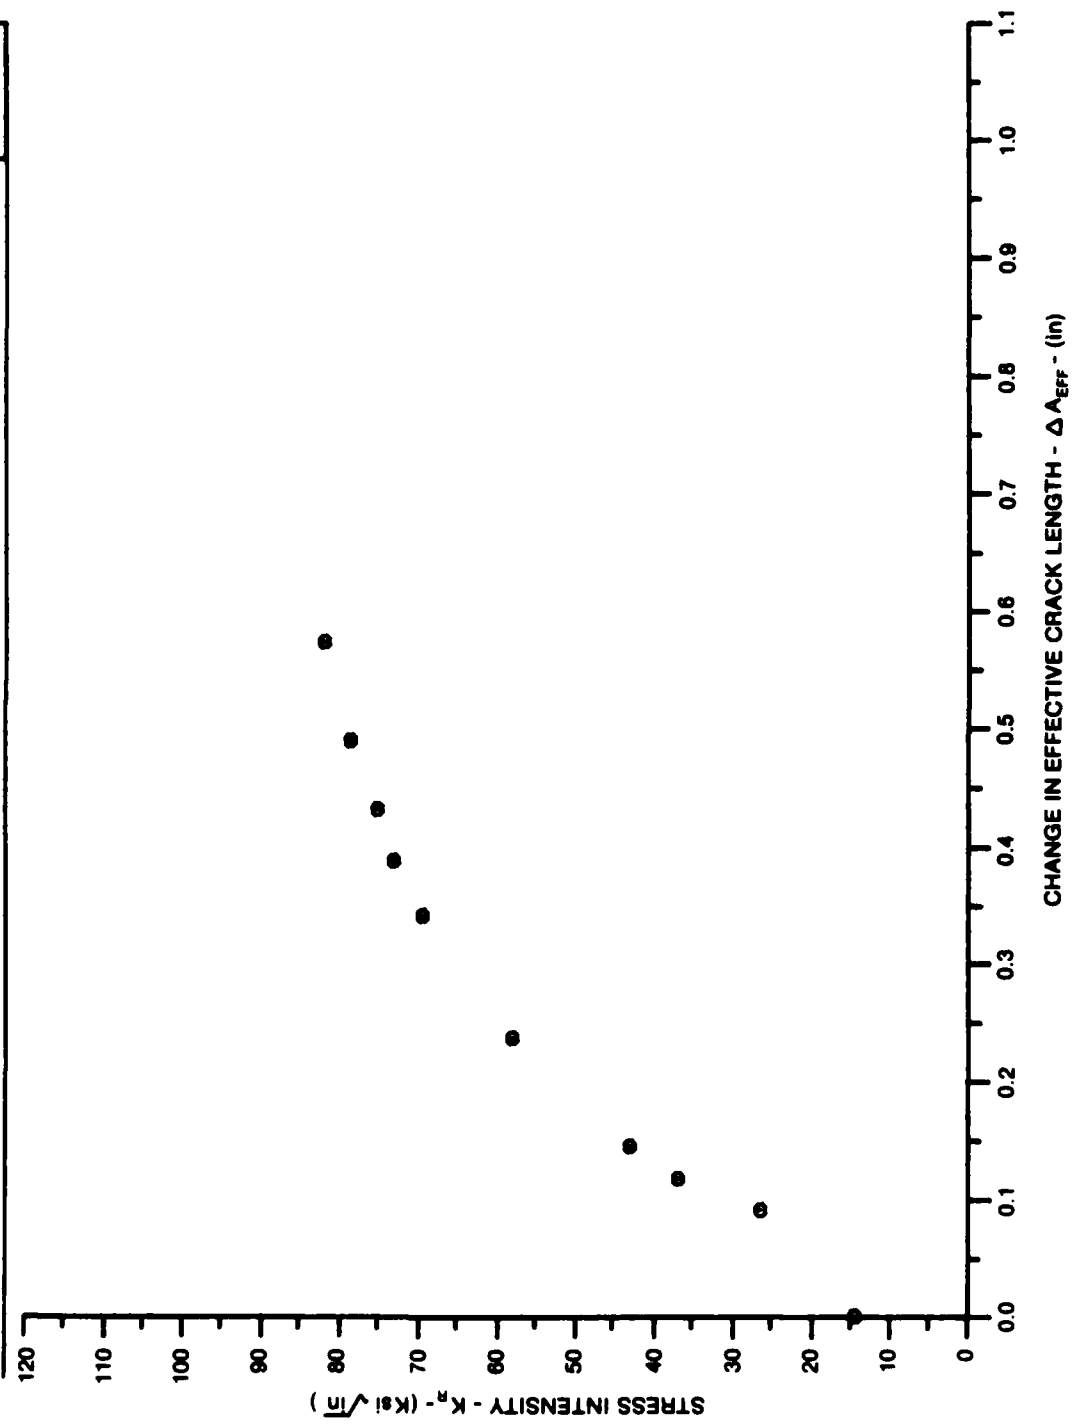


Figure 7.8.2.9

ALUM. ALLOY
2124

SPECIMEN THK: .482"
 SPECIMEN WIDTH: 6.828"
 K_{IC} (Ksi√in): 73.1
 REFERENCE: G0011

CONDITION/HT: T051
 FORM: 5.58" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T

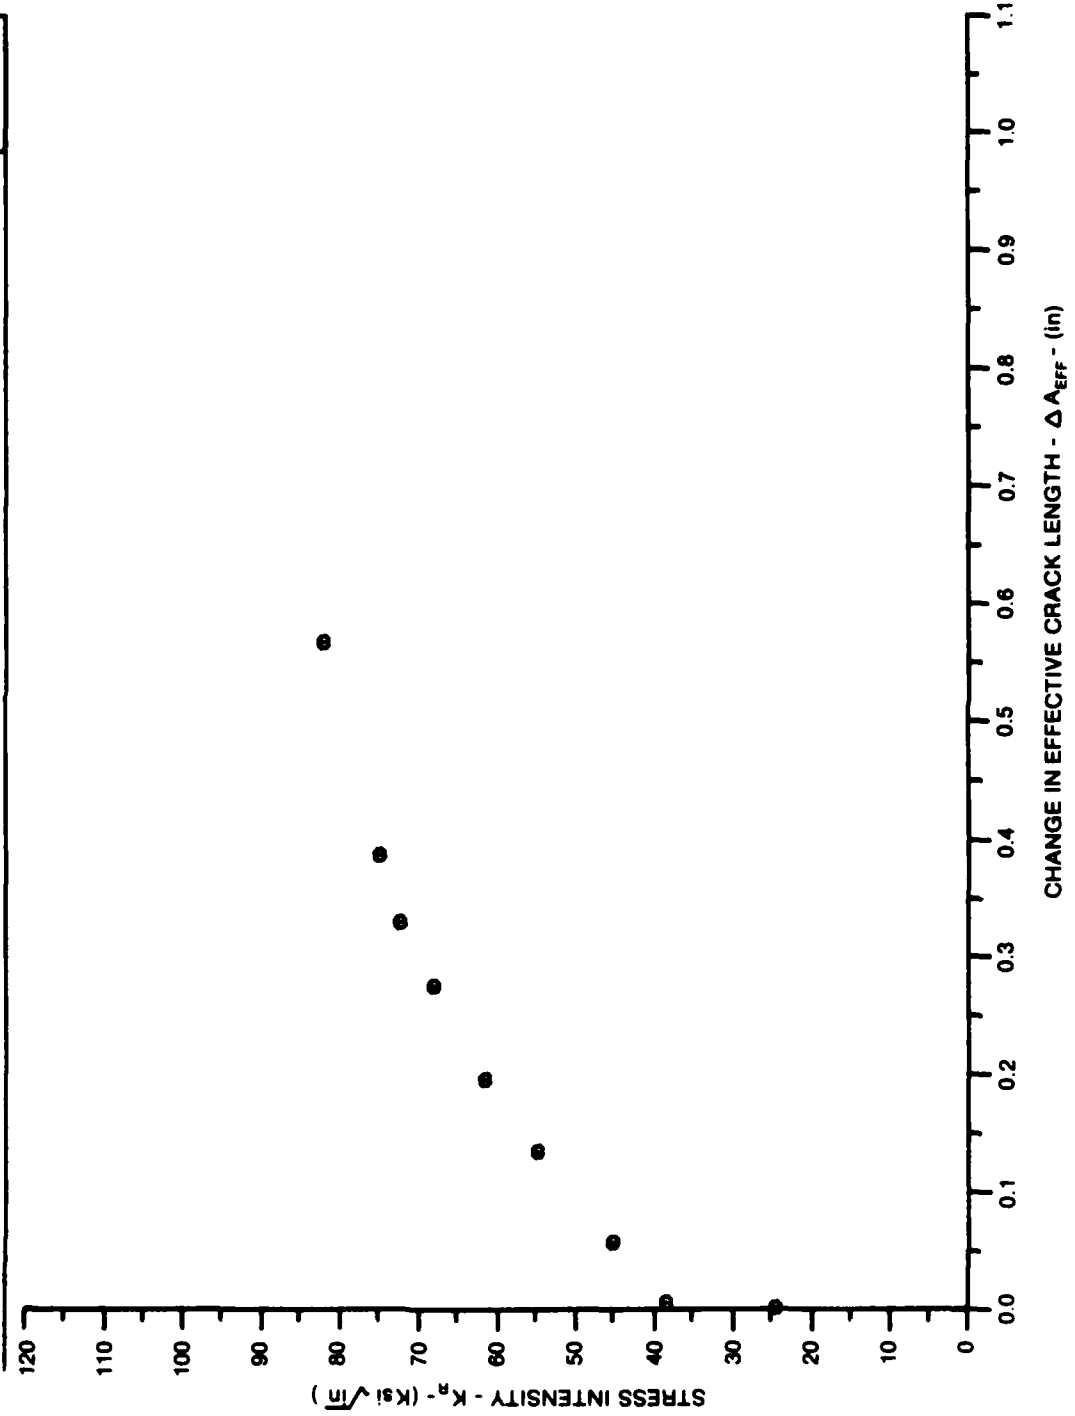


Figure 7.8.2.10

ALUM.
ALLOY

2124

SPECIMEN THK: .191"
SPECIMEN WIDTH: 5.800"
 K_{IC} (ksi√in): 53.8
REFERENCE: GD011

CONDITION/HT: T851
FORM: 5.00" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: T-L

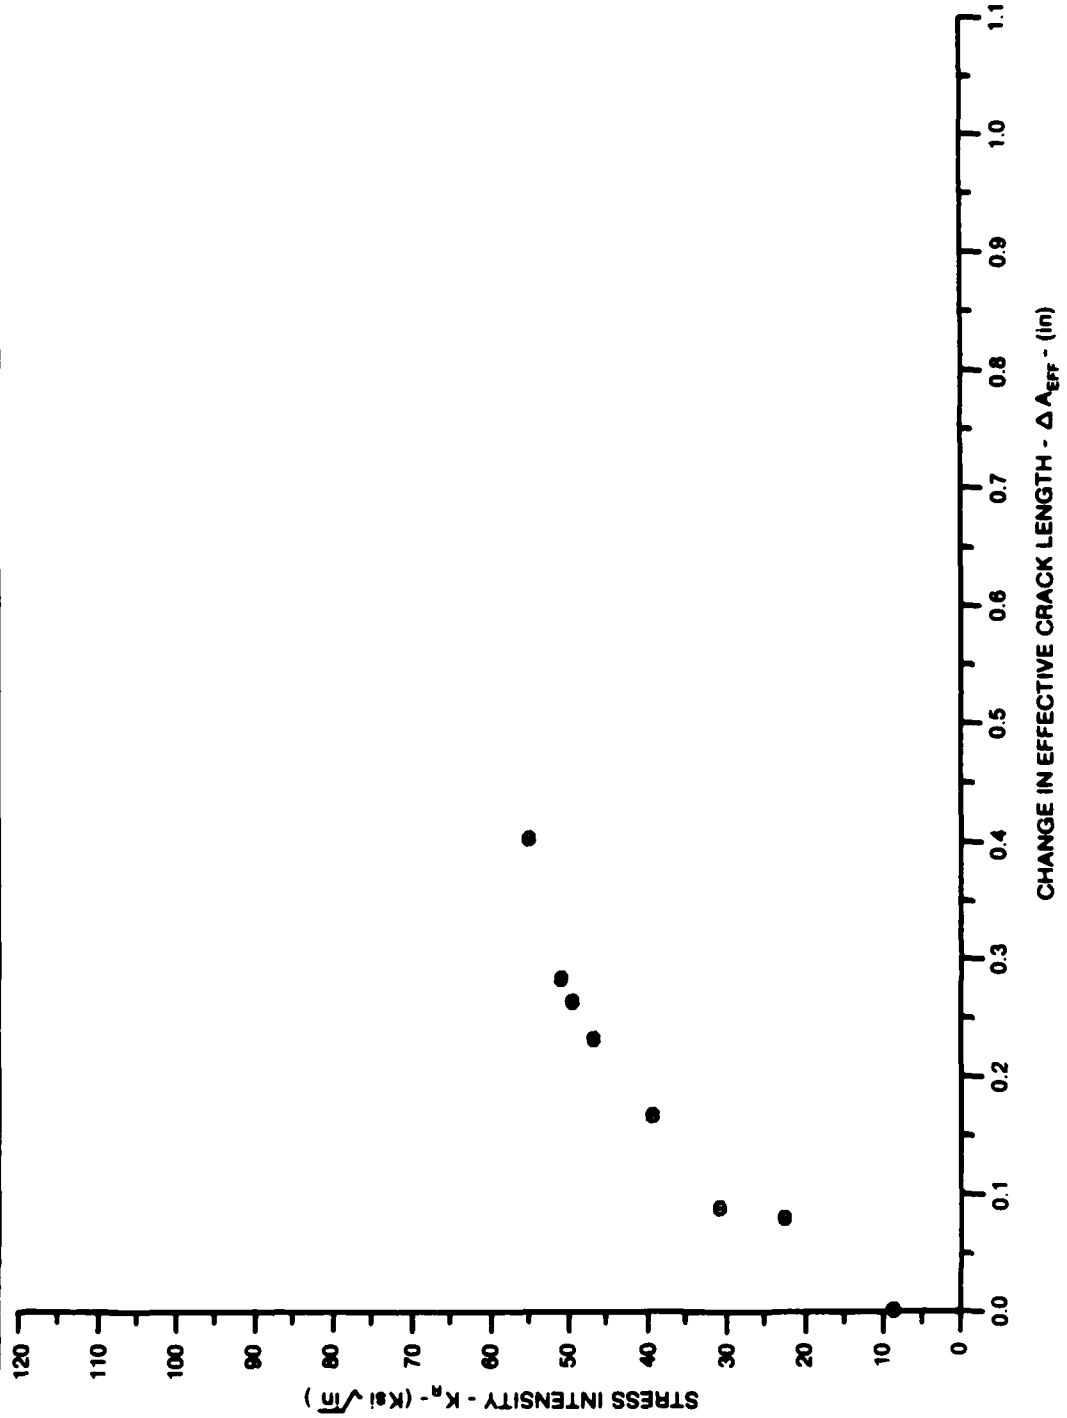


Figure 7.8.2.11

ALUM.
ALLOY

2124

SPECIMEN THK: .203"
SPECIMEN WIDTH: 5.825"
 K_{IC} (Ksi \sqrt{in}): 49.0
REFERENCE: GD811

CONDITION/HT: T851
FORM: 5.00" TH PLATE
SPECIMEN TYPE: CCP
ORIENTATION: T-L

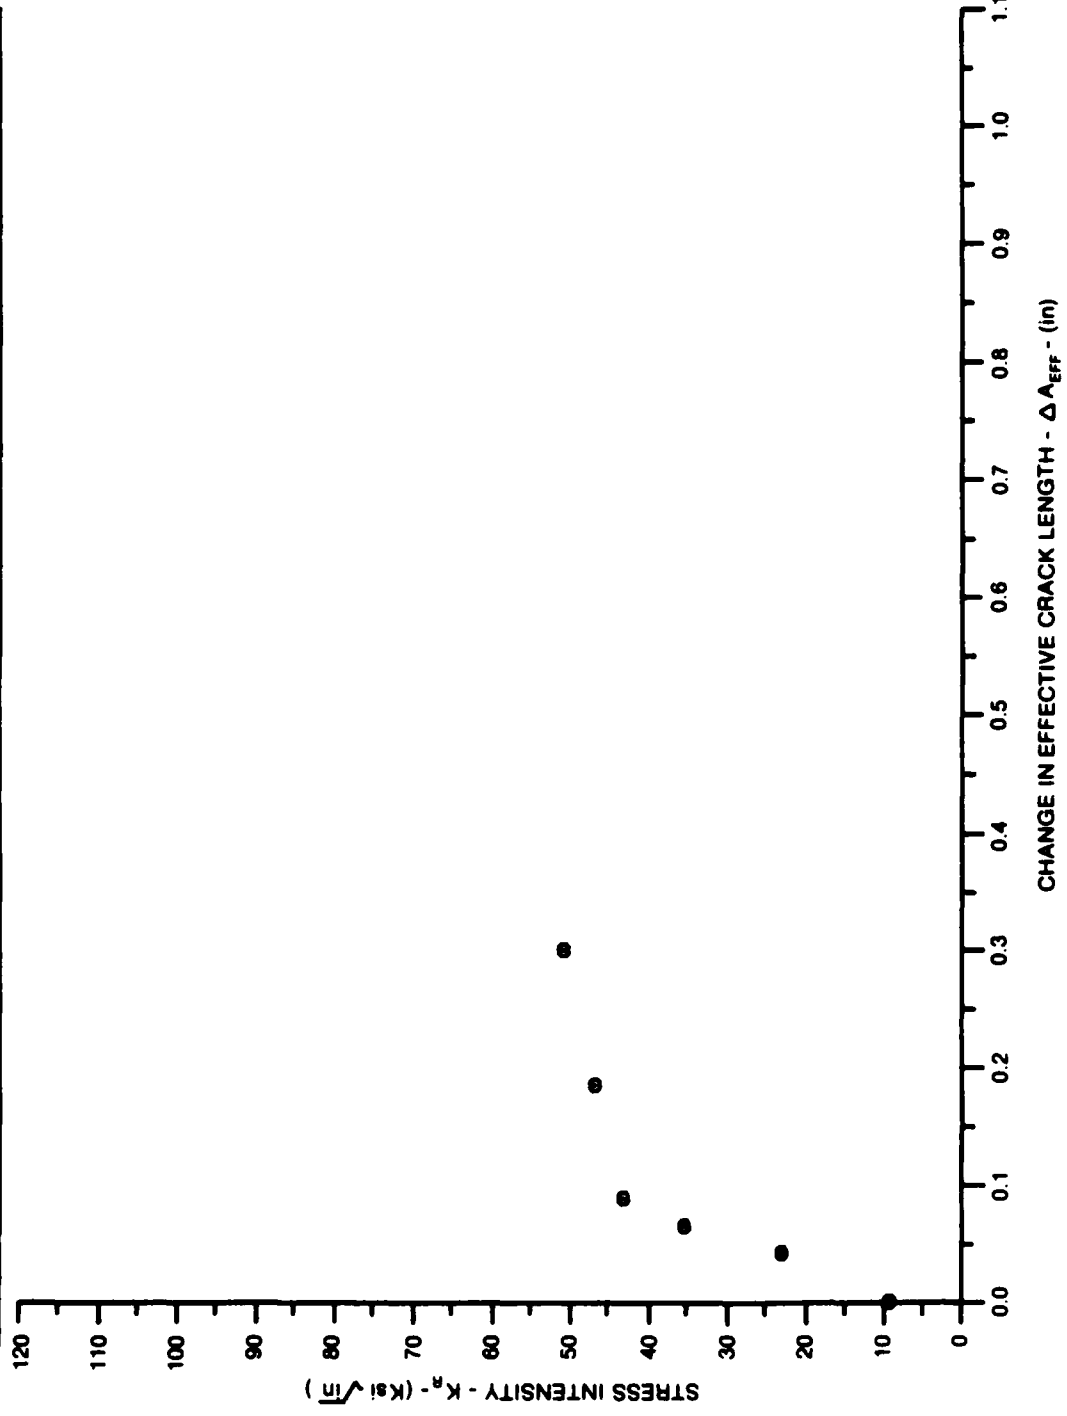


Figure 7.8.2.12

TABLE 7.8.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2124
CONDITION: T851
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.33			
DELTA K B:	A: 2.11	.00883			
MIN	C:				
	D:				
	2.50	.0441			
	3.00	.149			
	3.50	.317			
	4.00	.549			
	5.00	1.33			
	6.00	2.60			
	7.00	4.24			
	8.00	6.22			
	9.00	8.61			
	10.00	11.5			
	13.00	24.4			
	16.00	49.6			
	20.00	168.			
DELTA K B:	A: 20.19	182.			
MAX	C:				
	D:				

ROOT MEAN SQUARE 12.91
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: WDL
 ORIENTATION: L-T
 FREQUENCY: 25.00
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 66.0 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: NC003

ALUM.
ALLOY

2124

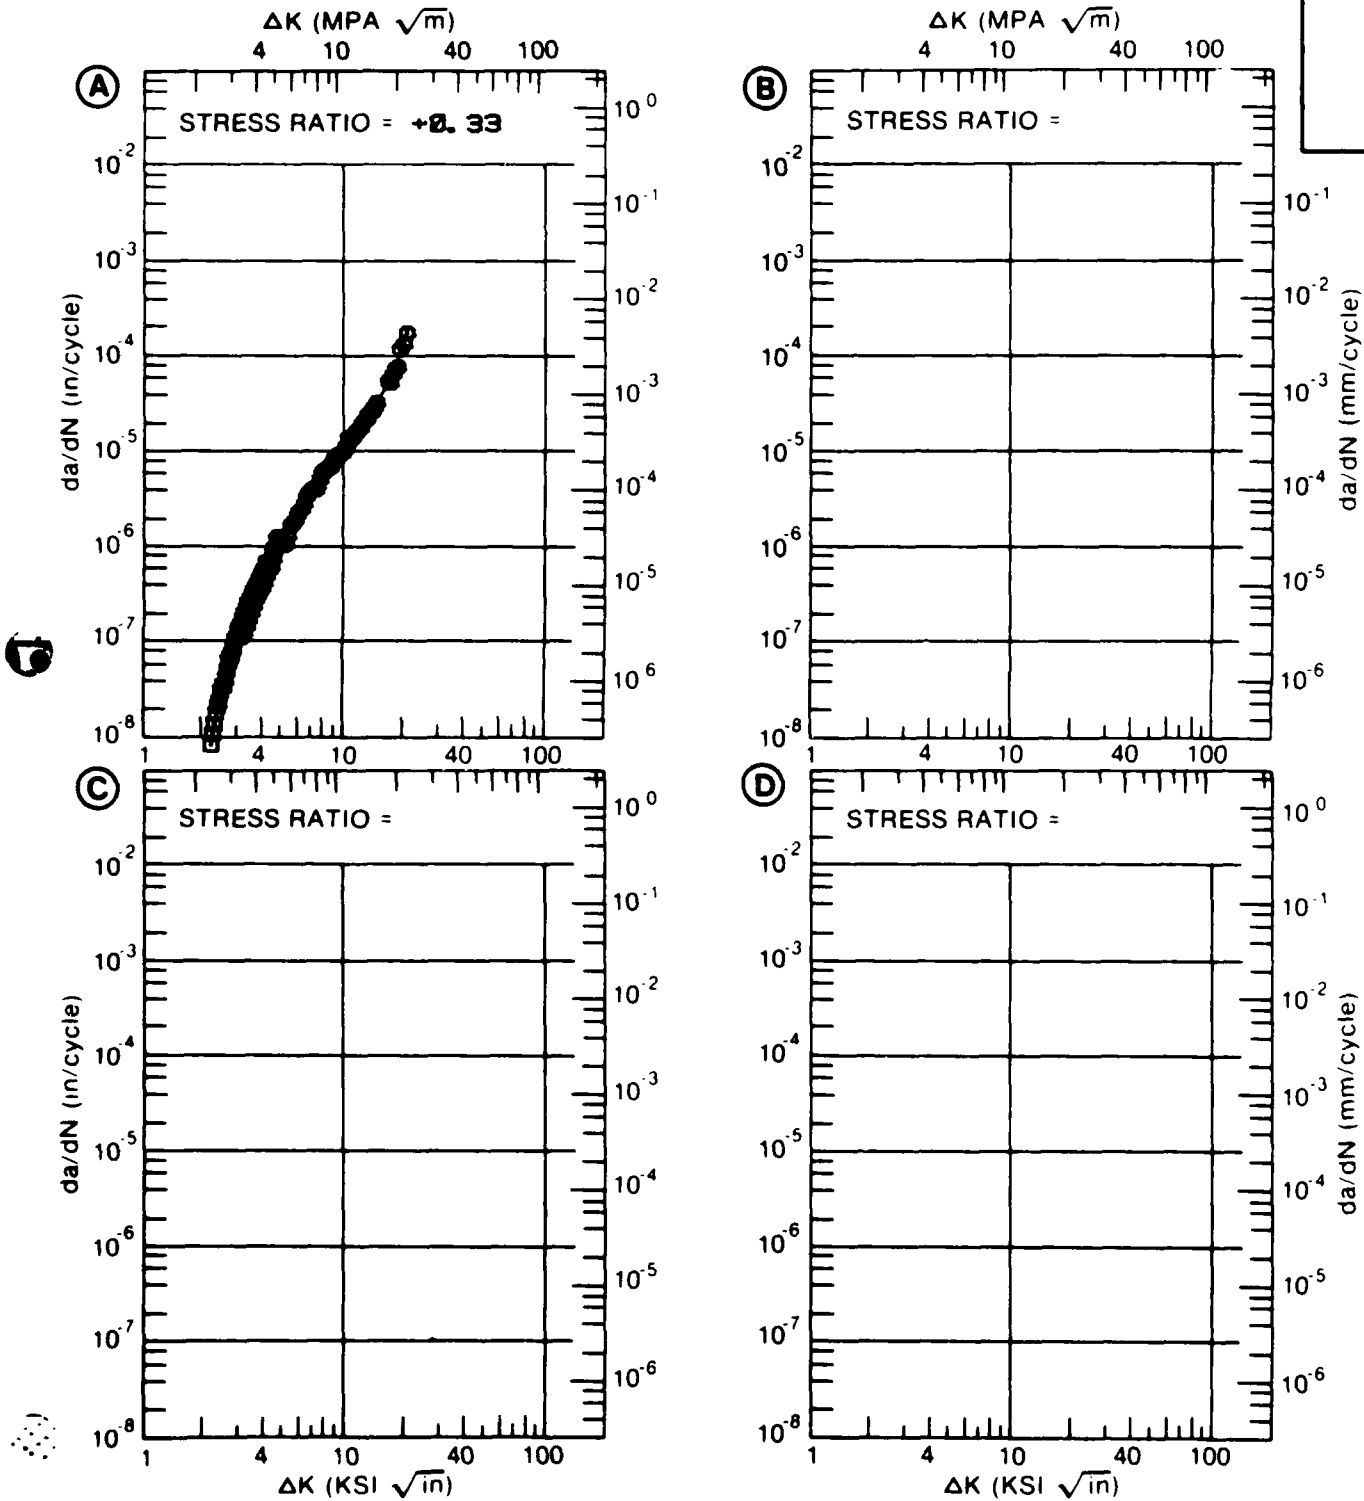


Figure 7.8.3.1

TABLE 7.8.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2124			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 2.05	.0155			
MIN	B:				
	C:				
	D:				
	2.50	.0474			
	3.00	.0874			
	3.50	.115			
	4.00	.142			
	5.00	.272			
	6.00	.596			
	7.00	1.11			
	8.00	1.80			
	9.00	2.70			
	10.00	3.84			
	13.00	9.39			
	16.00	20.7			
	20.00	56.7			
DELTA K	A: 22.02	93.8			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		32.48			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 1.50" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY: 1.00- 30.00 HZ

YIELD STRENGTH: 67.2 KSI
 ULT. STRENGTH: 71.5 KSI
 SPECIMEN THK: 0.109- 0.111"
 SPECIMEN WIDTH: 3.950- 3.954"
 REFERENCES: MA002

ALUM.
ALLOY

2124

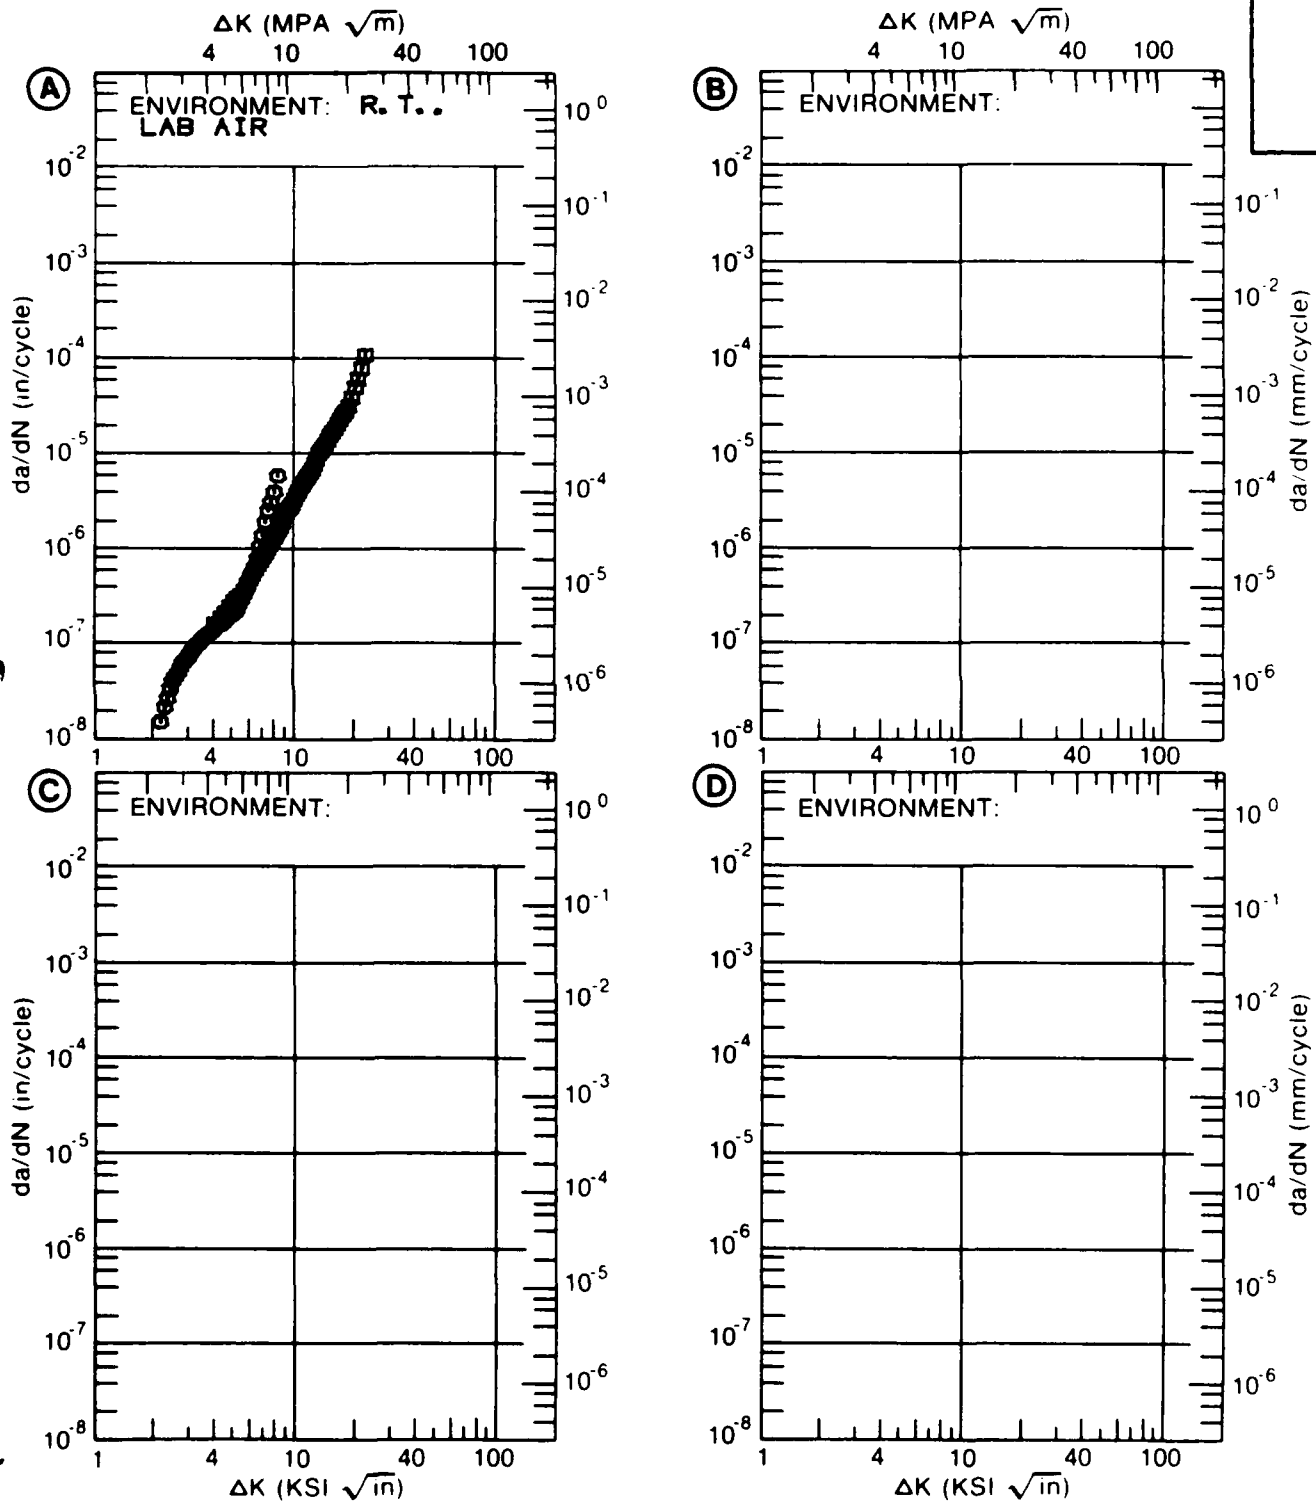


Figure 7.8.3.2

TABLE 7.8.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.3 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2124
CONDITION: T851
ENVIRONMENT: R. T., L. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	R=+0.10	R=+0.50		
DELTA K MIN				
A: 2.42	.0147			
B: 1.62		.00552		
C:				
D:				
2.00		.0501		
2.50	.0198	.0925		
3.00	.0661	.111		
3.50	.118	.173		
4.00	.163	.295		
5.00	.266	.682		
6.00	.458	1.16		
7.00	.776	1.78		
8.00	1.25	2.72		
9.00	1.89	4.29		
10.00	2.69	7.07		
13.00	6.60	34.6		
16.00	15.1	83.9		
20.00	44.6			
25.00	133.			
DELTA K MAX				
A: 26.67	174.			
B: 16.28		86.4		
C:				
D:				
ROOT MEAN SQUARE PERCENT ERROR	27.50	30.69		

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 30.00
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 86.4 KSI
 ULT. STRENGTH: 72.1 KSI
 SPECIMEN THK: 0.375- 1.500"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: U0005

ALUM.
 ALLOY

2124

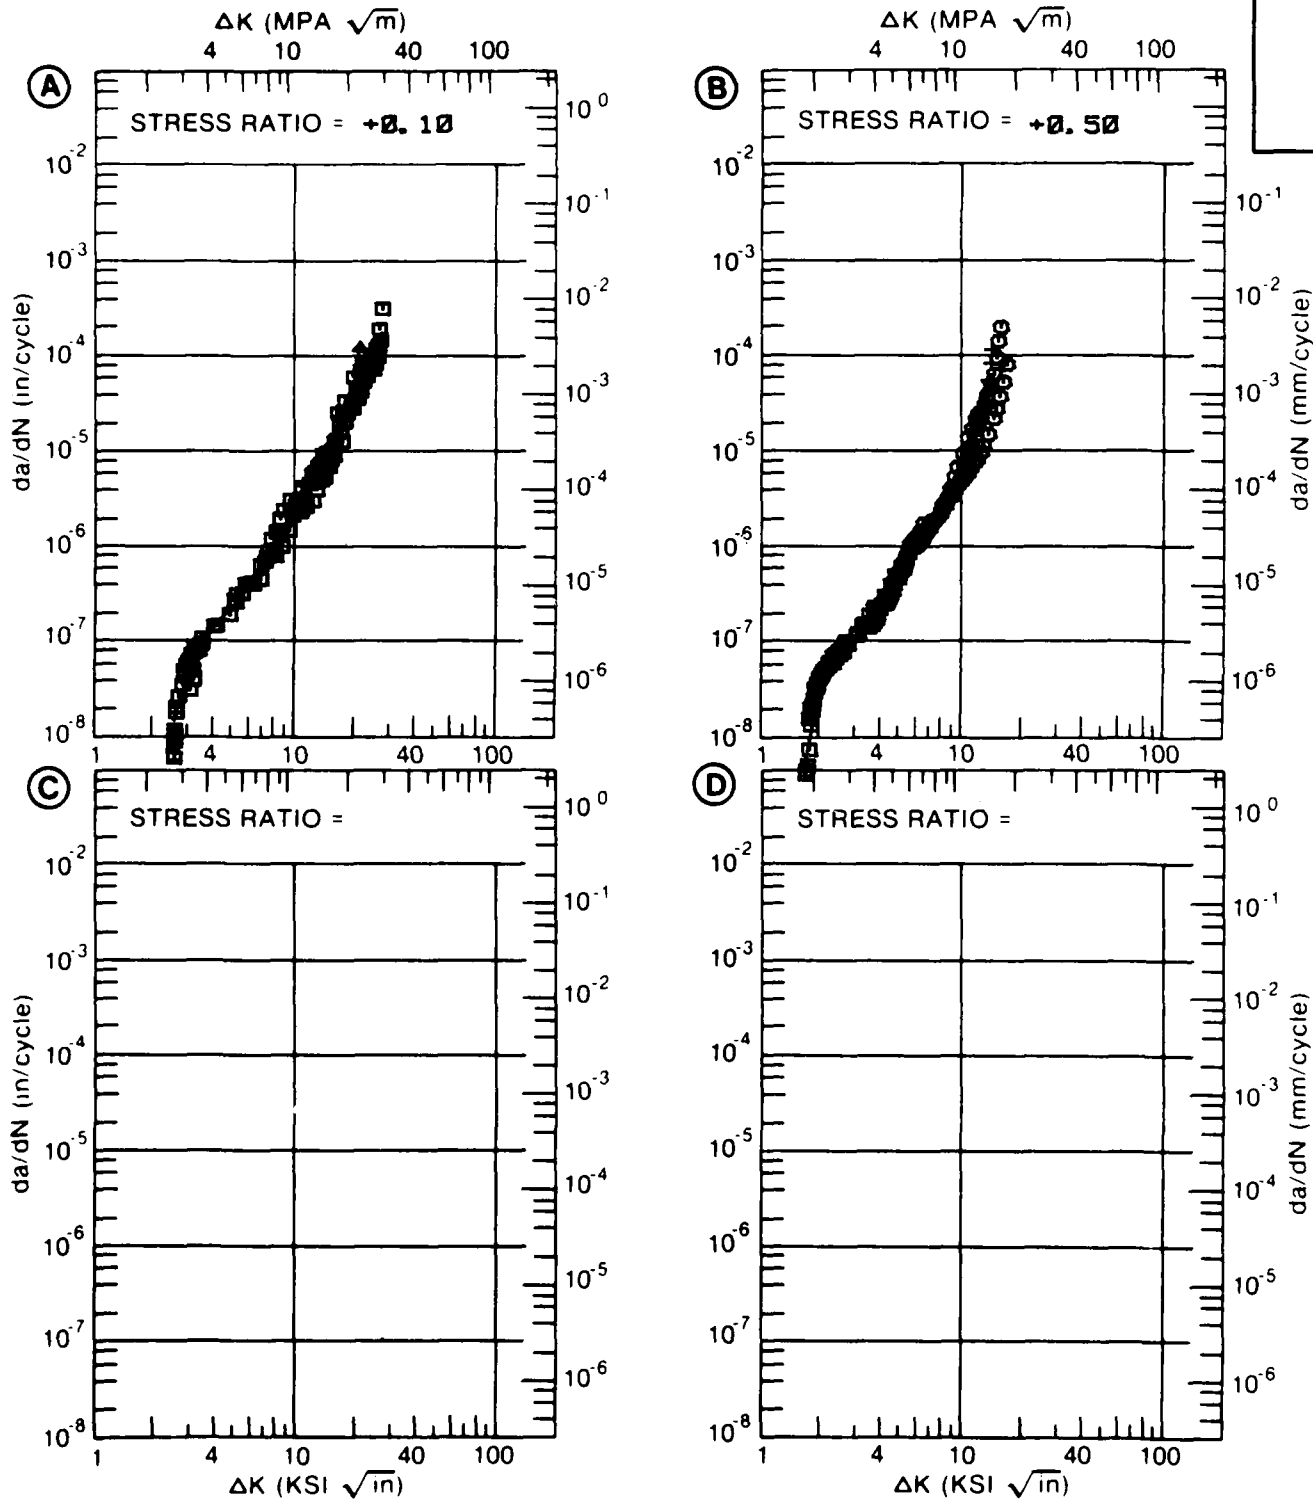


Figure 7.8.3.3

TABLE 7.8.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2124			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. SALT FOG		
DELTA K	A: 5.61	2.56			
MIN	B: 7.00		6.99		
	C:				
	D:				
	6.00	2.70			
	7.00	3.82	6.99		
	8.00	4.16	7.73		
	9.00	5.28	11.3		
	10.00	8.77	16.9		
	13.00	60.3	32.7		
DELTA K	A: 13.38	67.7			
MAX	B: 13.38		42.7		
	C:				
	D:				
ROOT MEAN SQUARE		13.83	6.22		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 4.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30

YIELD STRENGTH: 57.3 KSI
 ULT. STRENGTH: 64.1 KSI
 SPECIMEN THK: 1.489- 1.491"
 SPECIMEN WIDTH: 3.800"
 REFERENCES: 86842

ALUM.
 ALLOY
 2124

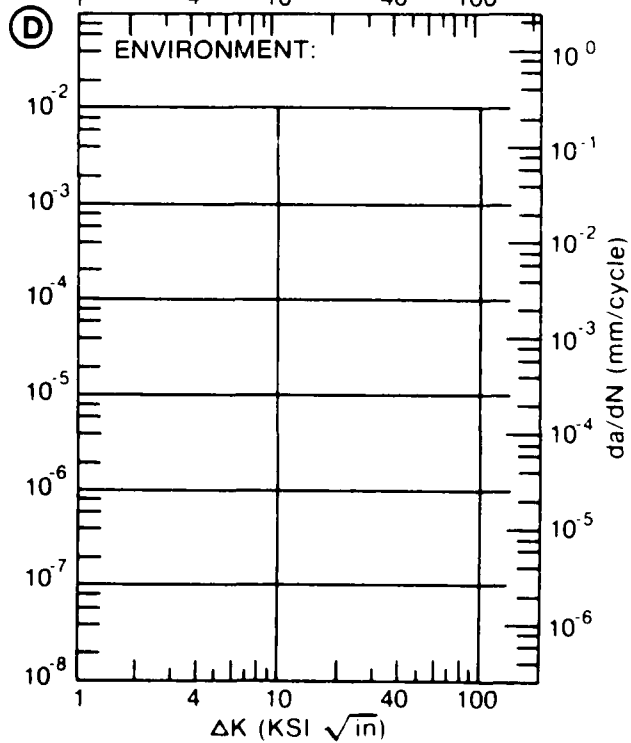
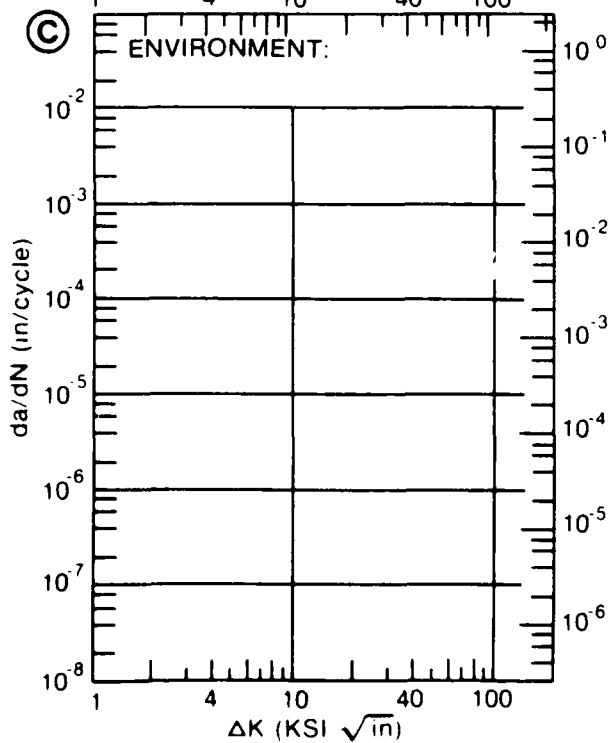
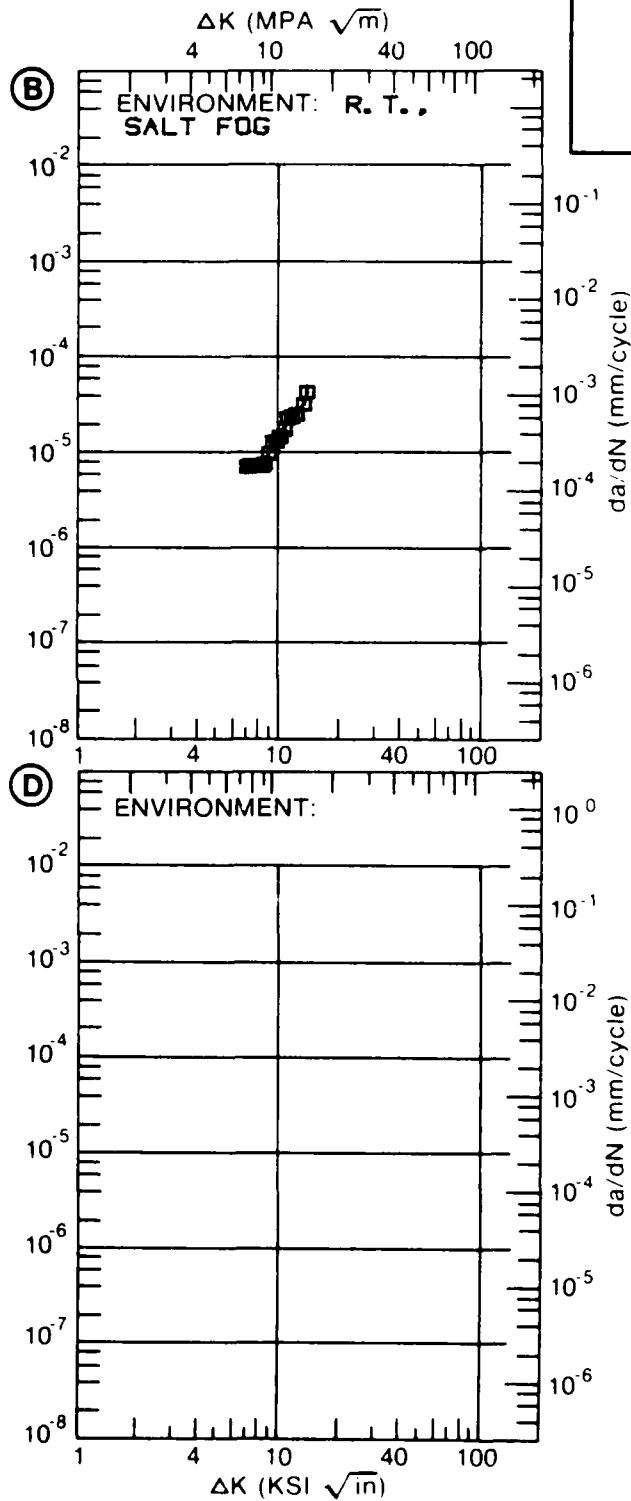
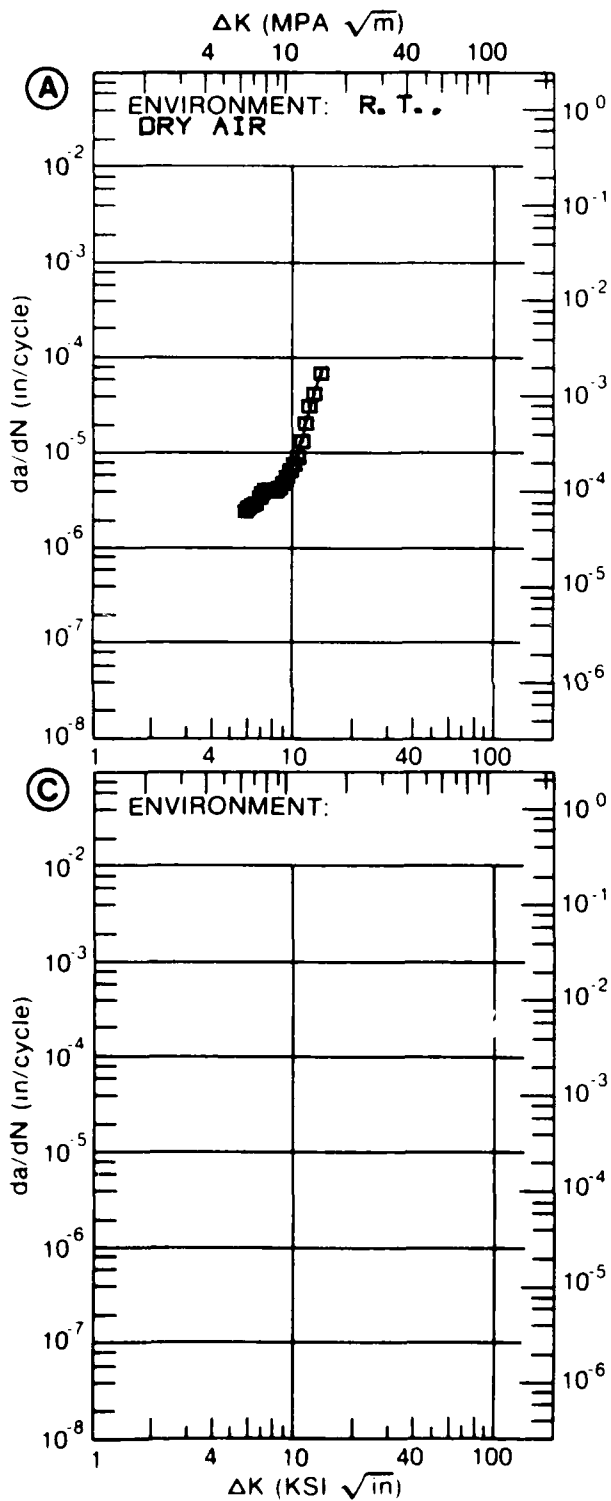


Figure 7.8.3.4

TABLE 7.8.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.5 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2124			
CONDITION: T851					
ENVIRONMENT: R. T., S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30	R=+0.50	
DELTA K MIN	A: 4.36	.105			
	B: 3.34		.135		
	C: 3.24			.199	
	D:				
	3.50		.143	.267	
	4.00		.219	.427	
	5.00	.265	.646		
	6.00	.458	1.45	1.07	
	7.00	1.16	2.63	2.27	
	8.00	2.48	4.17	3.64	
	9.00	4.15	6.08	5.16	
	10.00	6.04	8.37	7.02	
	13.00	12.6	17.9	9.52	
	16.00	22.2	33.5	27.1	
	20.00	50.4	119.		
	25.00	176.			
DELTA K MAX	A: 28.12	436.			
	B: 20.62		160.		
	C: 14.78			90.4	
	D:				
ROOT MEAN SQUARE		25.63	14.28	14.02	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25				
	1.25-2.0	1	2	2	
	>2.0	1			

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 62.6 KSI
 ULT. STRENGTH: 89.4 KSI
 SPECIMEN THK: 0.744- 0.750"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: GD003

ALUM.
 ALLOY
 2124

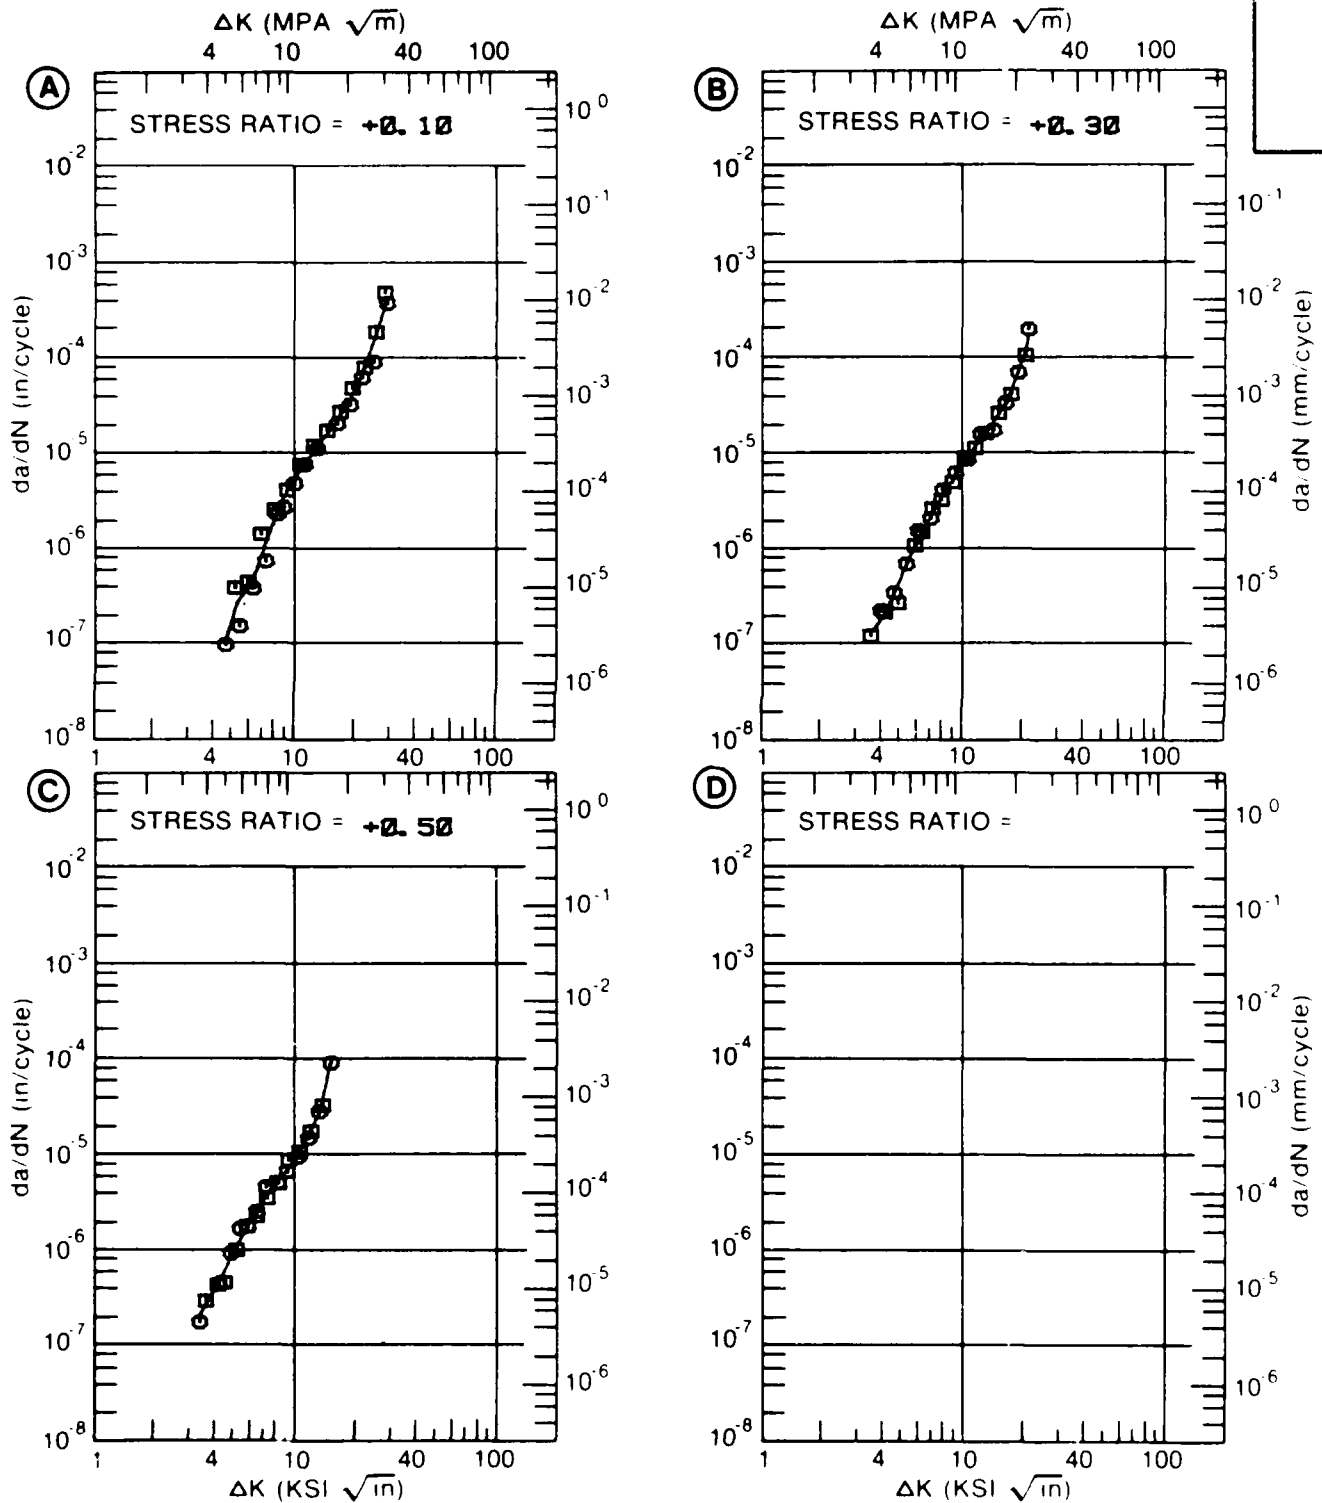


Figure 7.8.3.5

TABLE 7.8.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.6 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2124
CONDITION: T851
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.07			
DELTA K MIN	A:	2.71	.0317		
	B:				
	C:				
	D:				
		3.00	.0952		
DELTA K MAX	A:	3.12	.0627		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 38.48
PERCENT ERROR

LIFE	0.0-0.5	1
PREDICTION	0.5-0.8	1
RATIO	0.8-1.25	2
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY:
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 57.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: BL002

ALUM. ALLOY
2124




Figure 7.8.3.6

TABLE 7.8.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.7 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2124			
CONDITION: T851					
ENVIRONMENT: R. T. , H. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 25	R=+0. 50	
DELTA K MIN	A: 3. 20	. 050			
	B: 2. 03		. 007		
	C: 1. 79			. 045	
	D: 8				
	2. 00			. 0664	
	2. 50		. 0341	. 133	
	3. 00		. 0986	. 230	
	3. 50	. 0646	. 206	. 365	
	4. 00	. 105	. 353	. 553	
	5. 00	. 287	. 751	1. 17	
	6. 00	. 698	1. 29	2. 33	
	7. 00	1. 43	1. 99	4. 49	
	8. 00	2. 48	2. 95	8. 47	
	9. 00	3. 73	4. 27	15. 7	
	10. 00	5. 16	6. 15	28. 8	
	13. 00	12. 1	18. 5		
	16. 00	31. 1	58. 3		
DELTA K MAX	A: 16. 24	33. 8			
	B: 17. 43		102.		
	C: 12. 09			98. 9	
	D:				
ROOT MEAN SQUARE		35. 59	22. 28	17. 25	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0. 0-0. 5		1		
	0. 5-0. 8	1			
	0. 8-1. 25	6	3	5	
	1. 25-2. 0	5	4	3	
	>2. 0		1	3	

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 6.00- 33.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 63.2- 67.2 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 4.000- 6.000"
 REFERENCES: BL002

ALUM.
ALLOY

2124

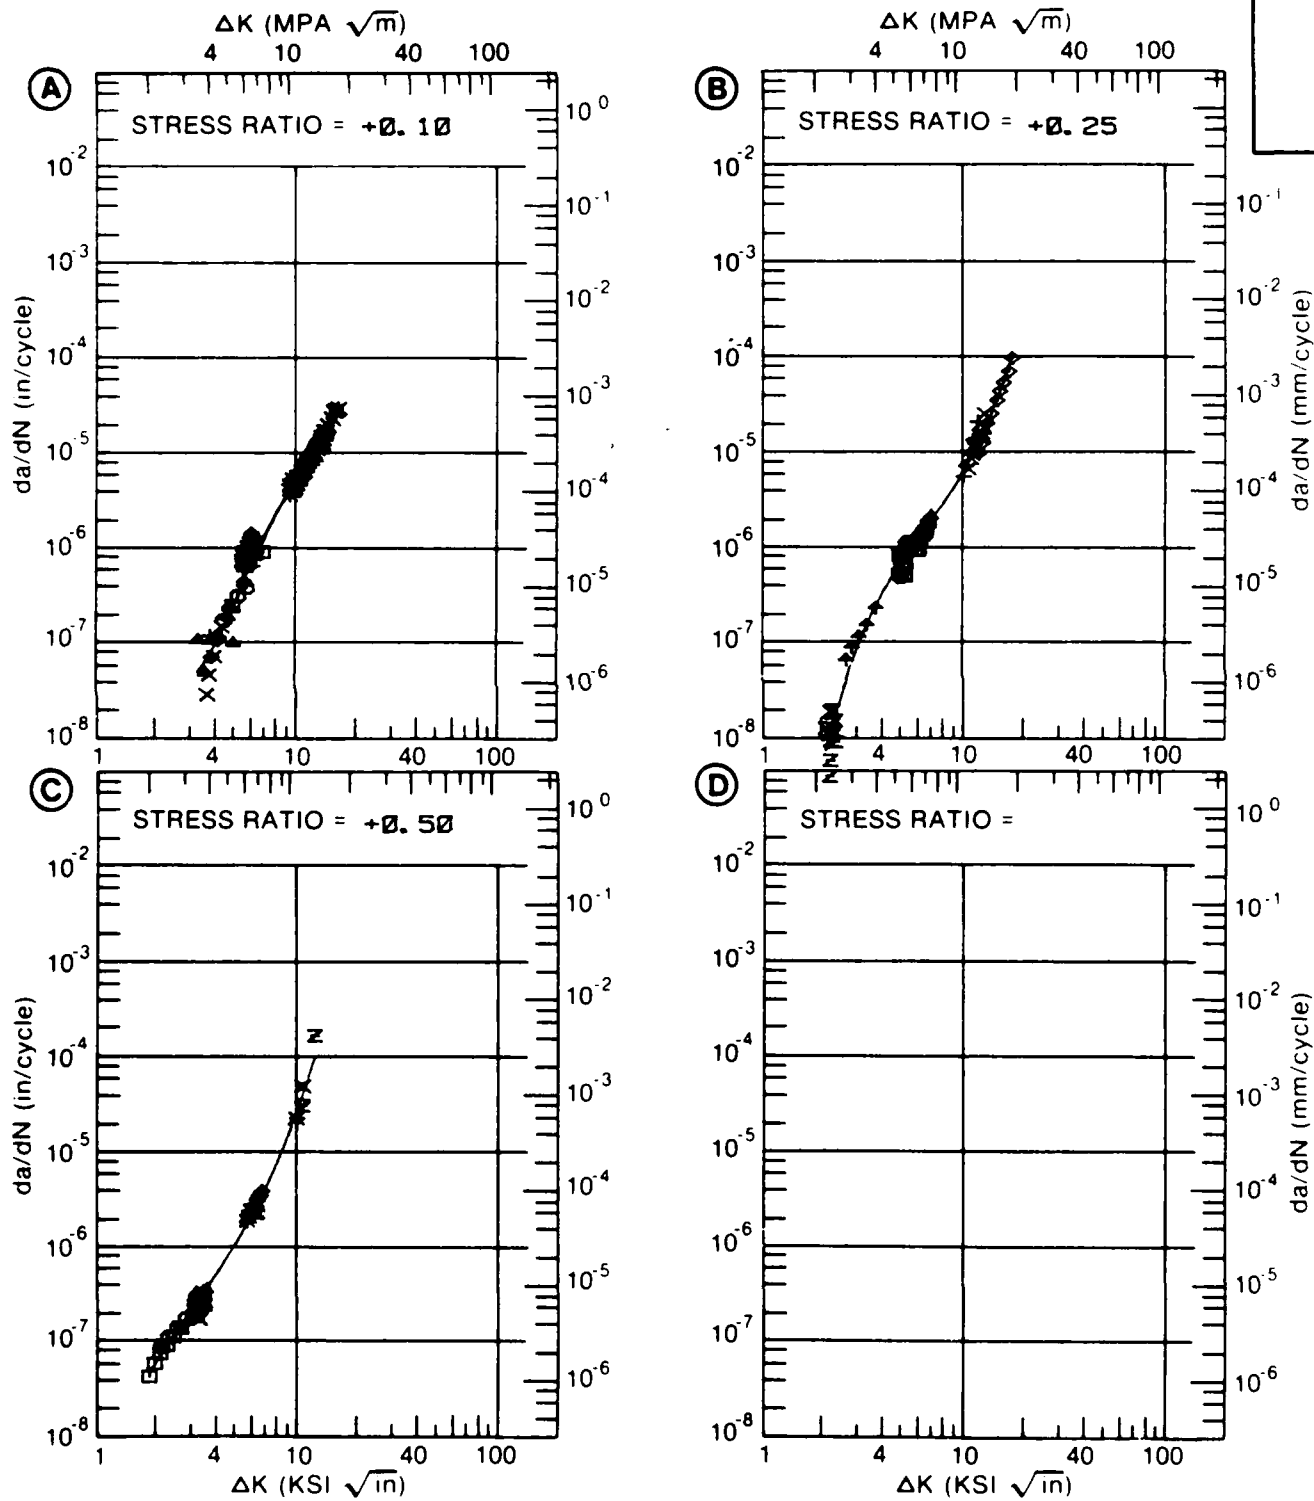


Figure 7.8.3.7

TABLE 7.8.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.8 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2124
CONDITION: T851
ENVIRONMENT: R. T. , H. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	R=+0.10	R=+0.50		
A: 4.28	.133			
B: 2.71		.0917		
C:				
D:				
3.00		.150		
3.50		.302		
4.00		.527		
5.00	.239	1.22		
6.00	.567	2.27		
7.00	1.19	3.73		
8.00	2.18	5.87		
9.00	3.60	9.23		
10.00	5.53	15.4		
13.00	15.0			
16.00	32.0			
20.00	92.9			
A: 23.19	473.			
B: 12.38		82.1		
C:				
D:				

ROOT MEAN SQUARE 17.19 10.35
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0 1
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.00
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 61.9 KSI
 ULT. STRENGTH: 89.0 KSI
 SPECIMEN THK: 0.750- 0.751"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: GD003

ALUM.
 ALLOY

2124

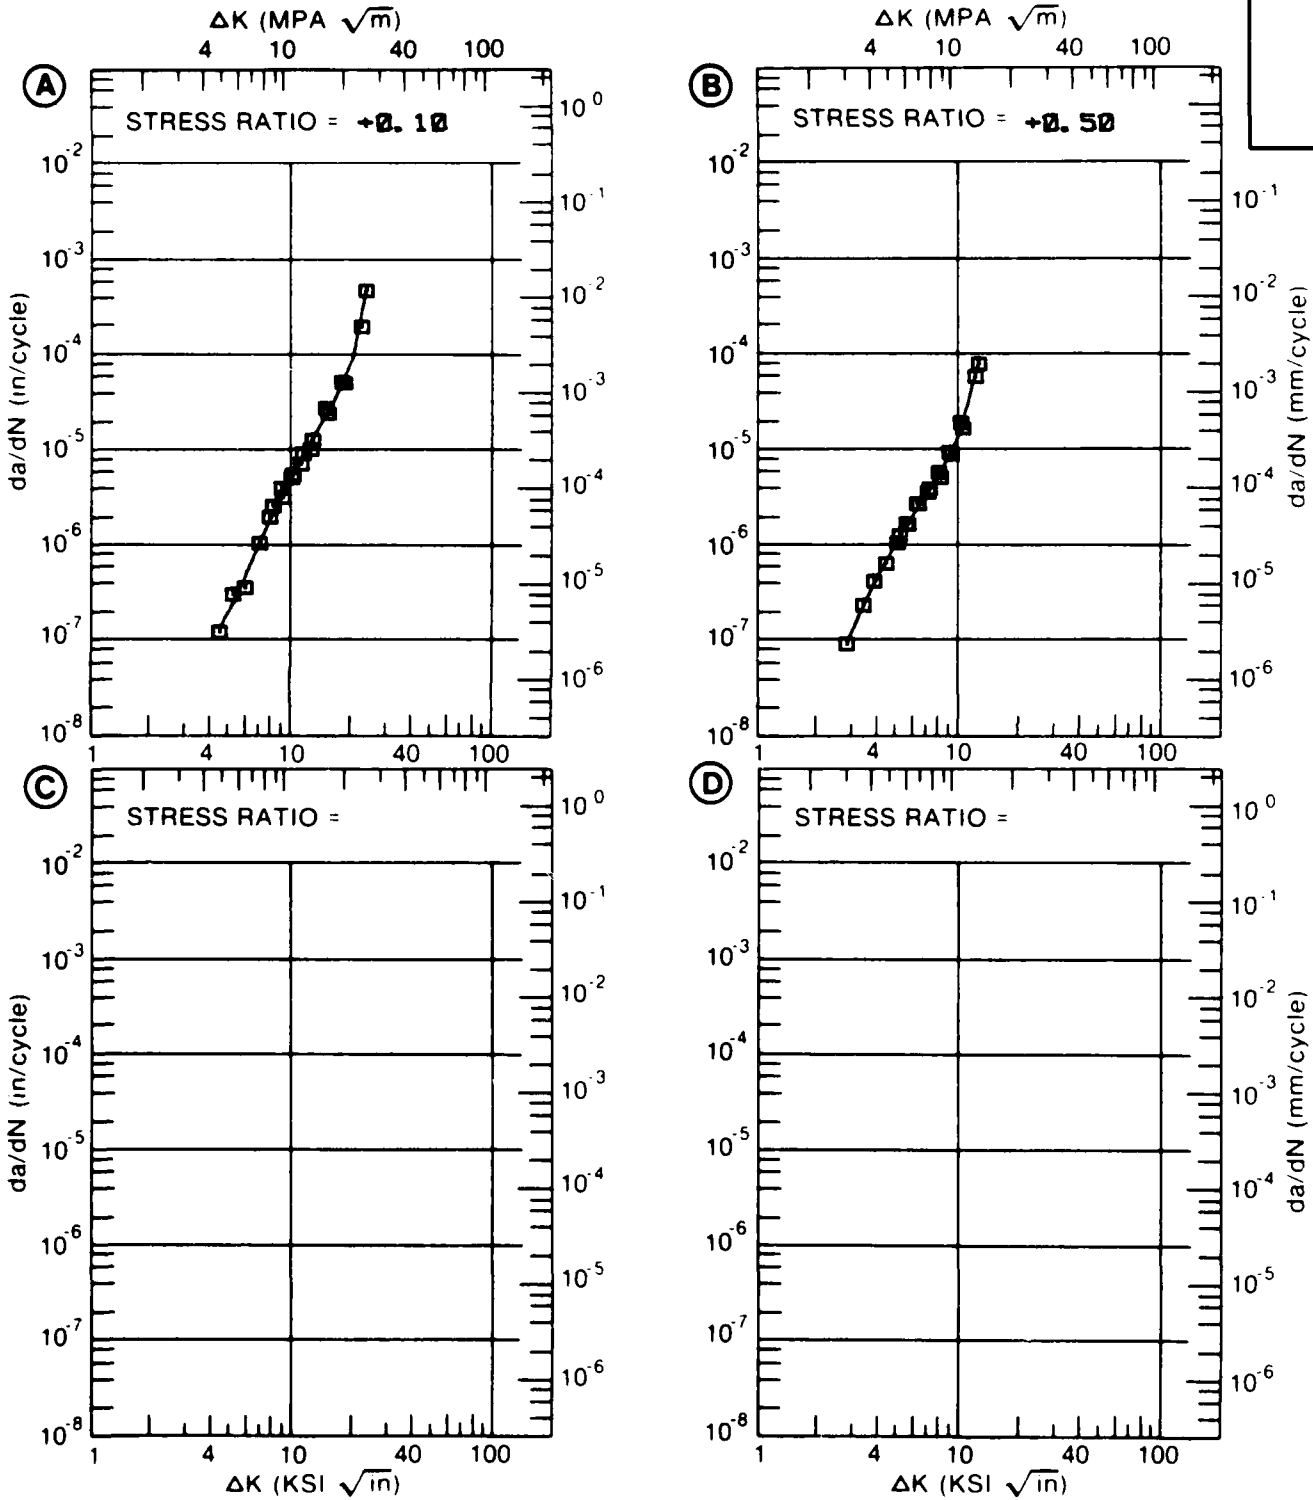


Figure 7.8.3.8

TABLE 7.8.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.9 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: ALUMINUM		2124			
CONDITION: T851					
ENVIRONMENT: R. T., S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.30	R=+0.50	
DELTA K A:	4.18	.240			
DELTA K B:	3.55		.214		
MIN C:	2.71			.157	
D:					
	3.00			.184	
	3.50			.278	
	4.00		.312	.443	
	5.00	.372	.595	1.08	
	6.00	.687	1.39	2.32	
	7.00	1.66	2.98	4.41	
	8.00	3.47	4.94	7.62	
	9.00	5.55	7.18	12.2	
	10.00	7.71	9.97	18.5	
	13.00	16.2	29.2		
	16.00	38.8			
DELTA K A:	19.20	140.			
B:	15.42		75.8		
MAX C:	12.15			80.0	
D:					
ROOT MEAN SQUARE		22.48	12.07	12.52	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0	2	2	2	
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.00
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 61.9 KSI
 ULT. STRENGTH: 69.0 KSI
 SPECIMEN THK: 0.748- 0.752"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: GD003

ALUM.
ALLOY

2124

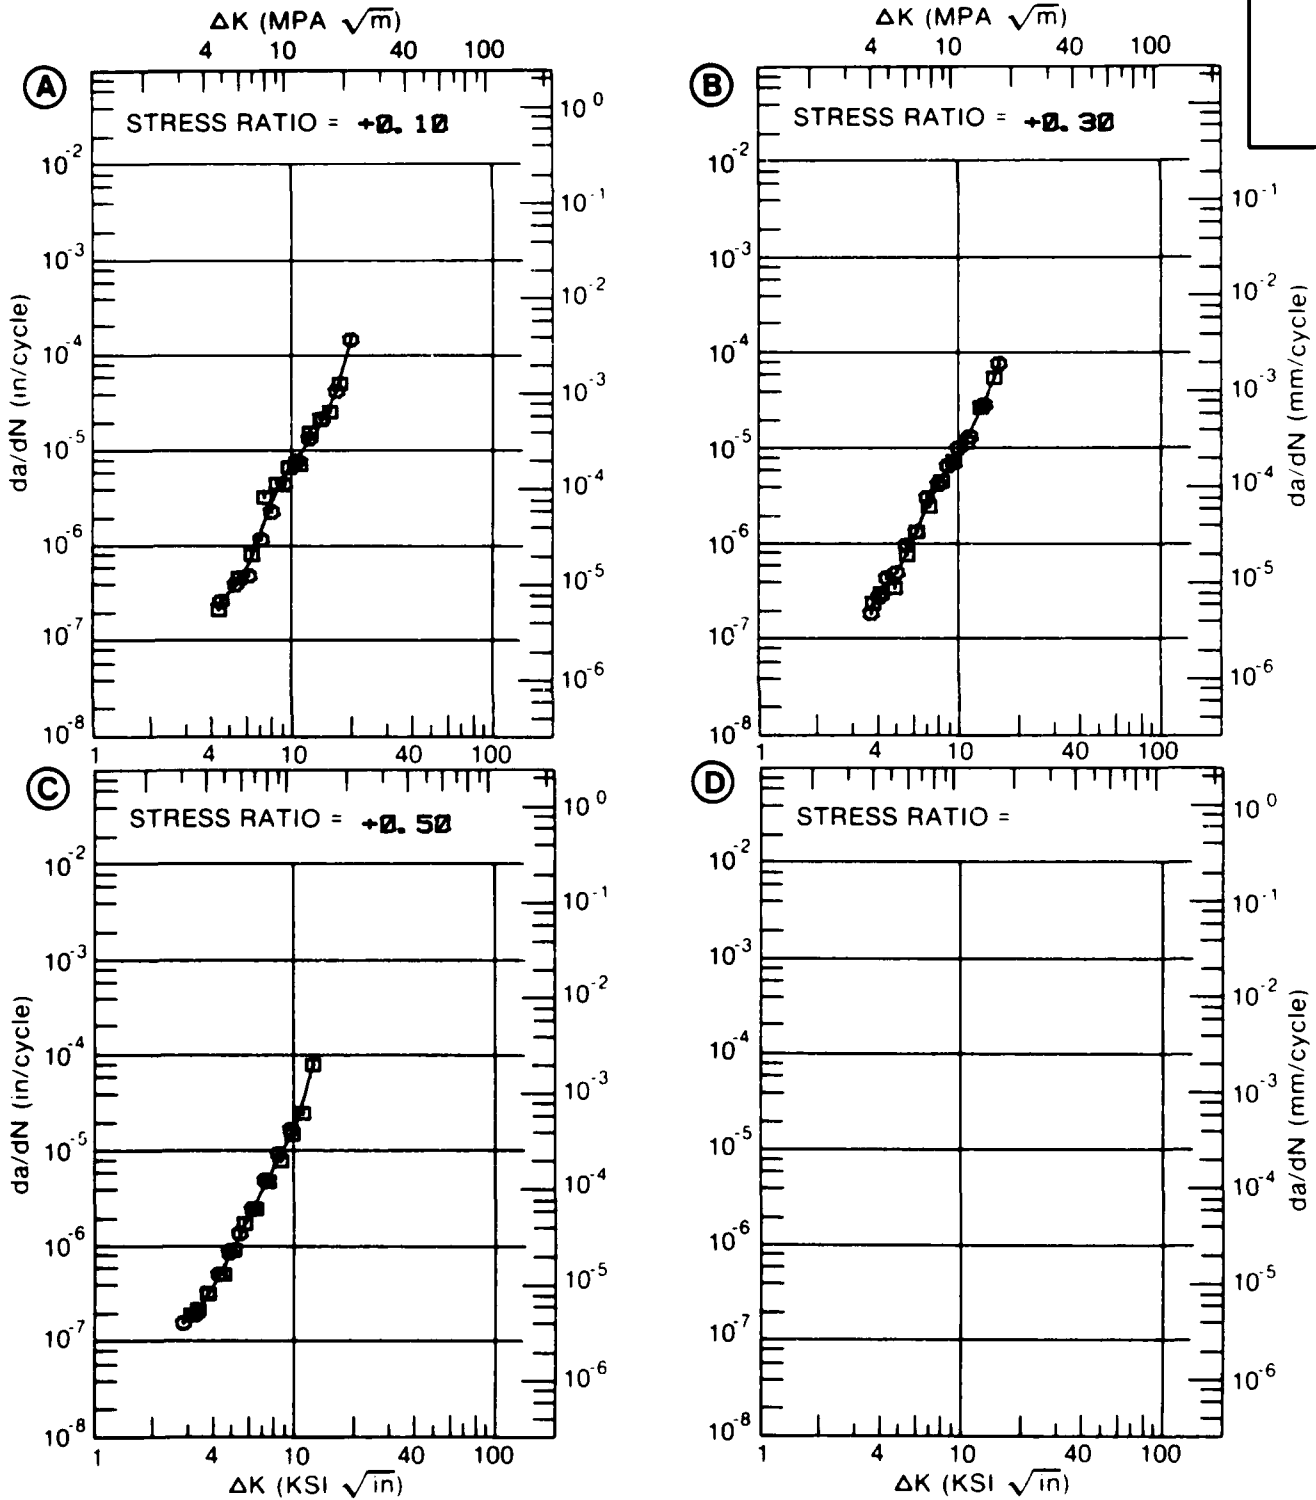


Figure 7.8.3.9

TABLE 7.8.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.8.3.10 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2124
CONDITION: T851
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0. 10	R=+0. 30	R=+0. 50	
A:	4. 52	. 285			
DELTA K B:	3. 72		. 392		
MIN C:	2. 67			. 198	
D:					
	3. 00			. 217	
	3. 50			. 336	
	4. 00		. 480	. 568	
	5. 00	. 444	. 949	1. 35	
	6. 00	. 962	1. 76	2. 60	
	7. 00	1. 81	3. 07	4. 48	
	8. 00	3. 10	5. 10	7. 21	
	9. 00	4. 96	8. 10	11. 4	
	10. 00	7. 59	12. 4	19. 4	
	13. 00	22. 3	36. 8	229.	
	16. 00	55. 1			
	20. 00	156.			
DELTA K A:	24. 53	443.			
B:	14. 61		60. 5		
MAX C:	13. 21			310.	
D:					
ROOT MEAN SQUARE		14. 59	12. 20	20. 50	
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25				
SUMMARY	1. 25-2. 0	2	2	2	
(NP/NA)	>2. 0				

CONDITION/HT: T851
 FORM: 5.50" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 59.1 KSI
 ULT. STRENGTH: 63.1 KSI
 SPECIMEN THK: 0.495- 0.501"
 SPECIMEN WIDTH: 3.990- 4.000"
 REFERENCES: GD003

ALUM.
ALLOY

2124

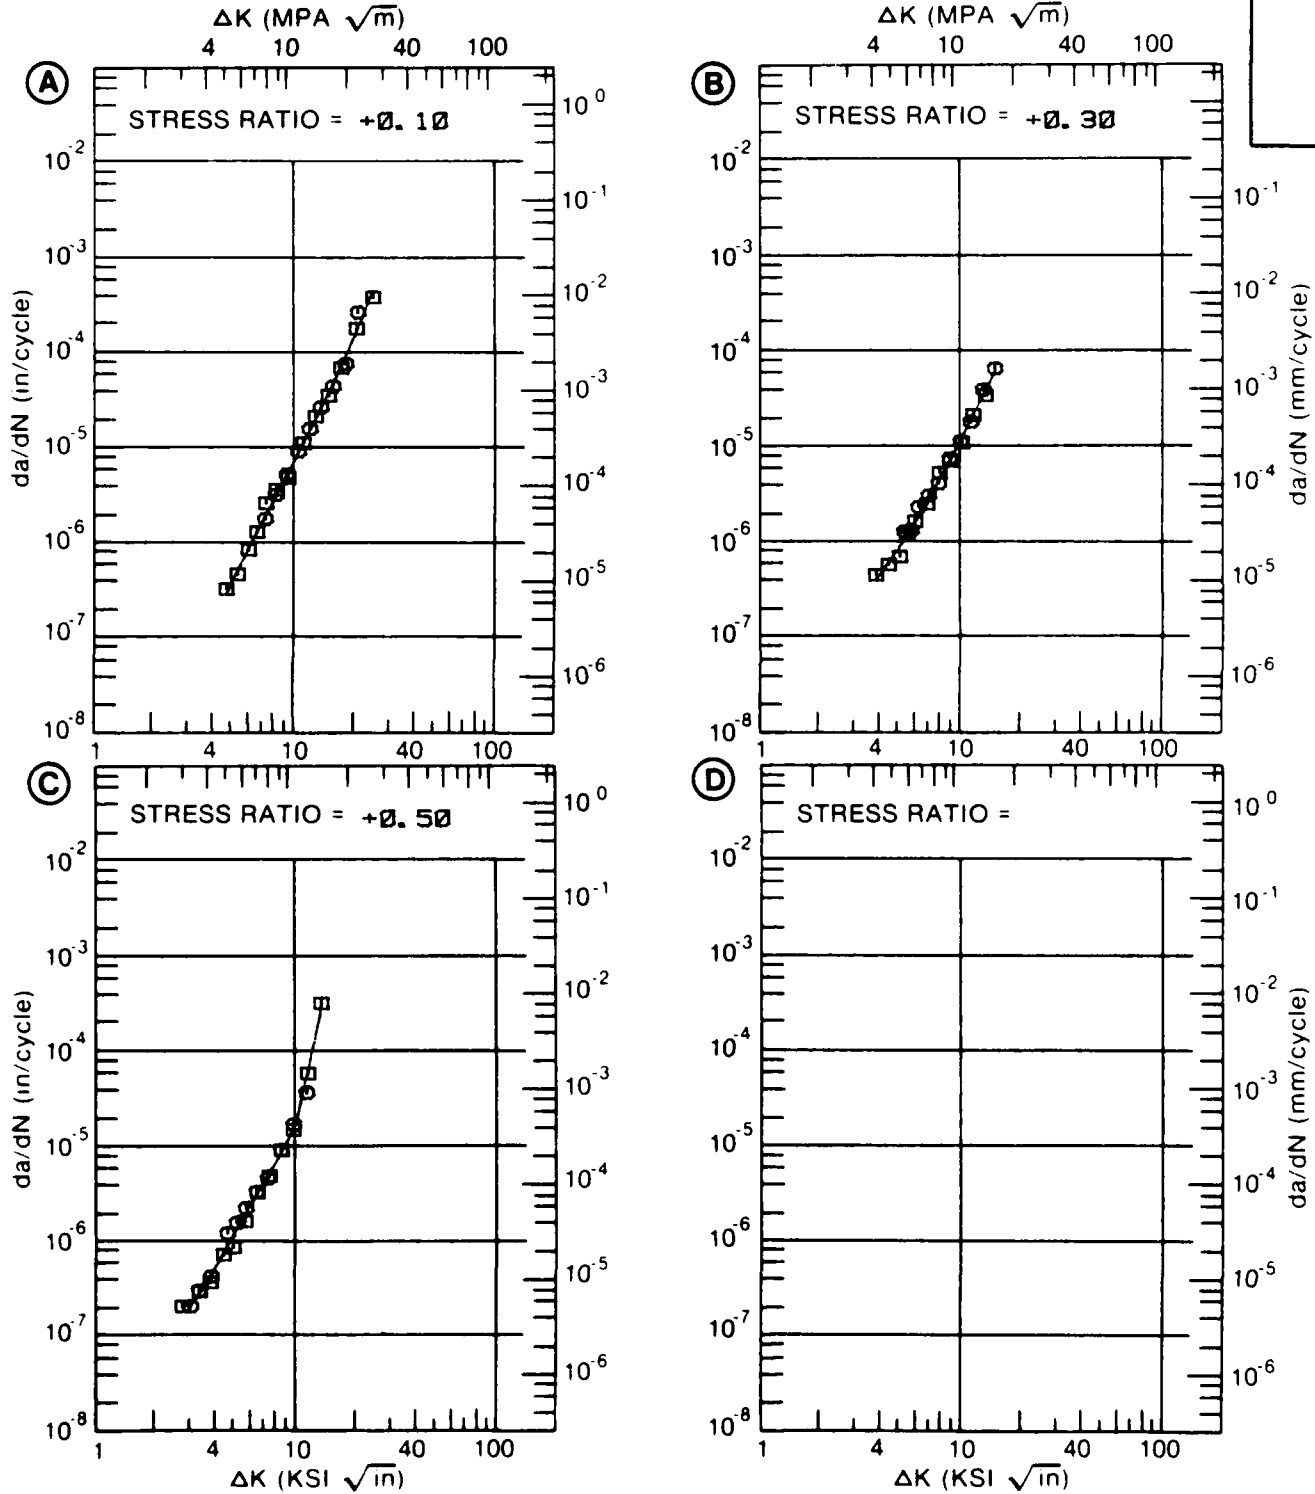


Figure 7.8.3.10

TABLE 7.8.3.11

ALUMINUM		2124		K (ISCC)												
CONDITION	--PRODUCT-- FORM THICK (IN)	TEST TEMP (F)	SPEC OR STR	YIELD (KSI)	ENVIRONMENT	WIDTH (IN)	THICK (IN)	DESIGN (**SQ)	CRACK LENGTH (IN)	K(8) (KSI*SQRT IN)	K (ISCC)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER	
																M
T851	P	3 00	R. T.	L-T	65.0	S. T. W.	5.500	1.000	DCB	---	41.00	27.80		70320	1976	RI006
		3 00			65.0		5.500	1.000	DCB	---	41.00	26.70		70320	1976	RI006
		3 00			65.0		5.500	1.000	DCB	---	41.00	> 26.00		60300	1976	RI006
							5.500	1.000	DCB	---	41.00	25.20	26.6/	54360	1976	RI006
T851	P	3 00	R. T.	S-L	63.0	B. T. W.	5.500	1.000	DCB	---	40.00	> 25.00		51720	1976	RI006
		3 00			63.0		5.500	1.000	DCB	---	40.00	21.00		54360	1976	RI006
		3 00			63.0		5.500	1.000	DCB	---	40.00	26.00		130620	1976	RI006
							5.500	1.000	DCB	---	40.00	21.00	22.7/	54360	1976	RI006
													1.3			

Table 7.9.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 2214 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KGT SORT(IN)) DEVIATION		(NUMBER OF SPECIMENS)	
	L-T	T-L	L-T	S-L
T651	35.3 ± 2.7 (11)	31.8 ± 0.9 (10)	-----	-----
T651 (417)	36.0 ± 3.4 (10)	29.4 ± 1.8 (15)	26.6 ± 1.8 (2)	

Table 7.9.2.1

CONDITION	--PRODUCT--		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	---SPECIMEN---			K(1C)	CRACK LENGTH (IN)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER	
	FORM	THICK (IN)			WIDTH (IN)	THICK (IN)	DESIGN								
															H
T651	P	1.75	R.T.	L-T	64.1	2.000	1.002	NB	0.963	0.75	35.10		1973	86213	
		1.75			64.1	2.000	1.002	NB	1.007	0.70	33.90		1973	86213	
		1.75			64.1	2.000	1.001	NB	0.955	0.70	34.00		1973	86213	
		1.75			64.3	2.000	1.002	NB	0.935	0.65	32.80		1973	86213	
		1.75			64.3	2.000	1.002	NB	0.955	0.63	32.40		1973	86213	
		1.75			64.3	2.000	1.002	NB	0.942	0.60	31.50		1973	86213	
		1.50			66.0	3.000	1.500	CT	1.638	0.80	37.30		1973	86213	
		1.50			66.0	3.000	1.500	CT	1.606	0.83	38.00		1973	86213	
		2.37			66.2	4.000	1.999	CT	1.977	0.70	35.00		1973	86213	
		1.50			66.4	3.000	1.499	CT	1.628	0.84	38.90		1973	86213	
T651		1.50			66.4	3.000	1.500	CT	1.602	0.90	39.90	35.3/	2.7	1973	86213
	P	1.75	R.T.	T-L	63.1	2.000	1.002	NB	0.985	0.67	32.70		1973	86213	
		1.75			63.1	2.000	1.001	NB	0.955	0.65	32.20		1973	86213	
		1.75			63.1	2.000	1.001	NB	1.048	0.67	32.60		1973	86213	
		1.75			63.2	2.000	1.001	NB	0.957	0.57	30.50		1973	86213	
		1.75			63.2	2.000	1.002	NB	1.033	0.64	32.00		1973	86213	
		1.75			63.2	2.000	1.001	NB	1.035	0.62	31.40		1973	86213	
		1.50			64.9	3.000	1.500	CT	1.576	0.58	31.20		1973	86213	
		1.50			64.9	3.000	1.499	CT	1.567	0.56	30.60		1973	86213	
		1.50			65.2	3.000	1.500	CT	1.597	0.64	32.90		1973	86213	
T651		1.50			65.2	3.000	1.500	CT	1.589	0.60	31.90	31.8/	0.9	1973	86213
	P	1.50	84	B-L	62.7	1.000	0.500	CT	0.483	0.33	22.90		1973	86213	
		1.50			62.7	1.000	0.500	CT	0.495	0.39	24.90		1973	86213	
T651 (417)		1.50			64.6	0.990	0.500	CT	0.492	0.33	23.30		1973	86213	
		1.50			64.6	1.000	0.500	CT	0.485	0.37	25.00	24.0/	1.1	1973	86213
	P	2.00	R.T.	L-T	63.9	3.000	1.500	CT	1.560	0.85	37.20		1973	86213	
		2.00			63.9	3.000	1.500	CT	1.586	0.89	38.20		1973	86213	
		3.00			64.8	3.000	1.500	CT	1.584	0.79	36.90		1973	86213	
		1.75			64.9	3.000	1.501	CT	1.533	1.15	44.10		1973	86213	
		2.37			66.2	4.000	1.998	CT	2.046	0.71	35.50		1973	86213	
T651		2.25			66.3	4.000	1.998	CT	2.123	0.68	34.70		1973	86213	
		3.93			66.3	3.000	1.500	CT	1.464	0.65	33.80		1973	86213	
		2.25			66.3	4.000	1.998	CT	2.021	0.67	34.40		1973	86213	
	3.93			66.3	3.000	1.501	CT	1.444	0.60	32.60		1973	86213		

Table 7.9.2.1 (Con't)

CONDITION	ALUMINUM		2214		K(IIC)		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	PRODUCT THICK (IN)	W	SPECIMEN		CRACK LENGTH (IN)	2.5* (K(IIC)/TYS)**2 (IN)	P (KSI*SQRT IN)	K(IIC) MEAN DEV (IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)	WIDTH (IN)	THICK (IN)	DESIGN	A						B								
T651 (417)	P	2 25	R T	L-T	4.000	1.998	CT	2.047	0.62	33.00	36.0/	3.4	1973	86213						
T651 (417)	P	3 00	R T	T-L	3.000	1.500	CT	1.540	0.49	27.70			1973	86213						
		3 00			3.000	1.501	CT	1.549	0.53	28.90			1973	86213						
		2 00			3.000	1.501	CT	1.592	0.57	30.10			1973	86213						
		2 00			3.000	1.501	CT	1.568	0.55	29.60			1973	86213						
		1 50			3.000	1.501	CT	1.598	0.58	30.60			1973	86213						
		1 50			3.000	1.491	CT	1.606	0.62	31.60			1973	86213						
		2 25			4.010	1.999	CT	2.122	0.47	27.90			1973	86213						
		1 75			3.000	1.500	CT	1.623	0.63	32.30			1973	86213						
		2 25			4.000	1.999	CT	2.141	0.43	26.60			1973	86213						
		2 25			4.000	1.999	CT	2.126	0.46	27.40			1973	86213						
		2 25			4.000	1.998	CT	2.179	0.48	28.00			1973	86213						
		2 37			4.000	1.999	CT	2.093	0.48	28.40			1973	86213						
		2 37			4.000	1.998	CT	2.150	0.48	28.40			1973	86213						
		3 93			3.000	1.501	CT	1.484	0.58	31.30	29.4/	1.8	1973	86213						
		3 93			3.000	1.500	CT	1.484	0.60	31.70			1973	86213						
T651 (417)	P	3 00	R T	S-L	2.000	1.001	CT	0.962	0.45	25.30			1973	86213						
		3 93			3.000	1.500	CT	1.532	0.52	27.90	26.6/	1.8	1973	86213						
T651 (417)	P	1 50	82	S-L	1.000	0.499	CT	0.486	0.41	24.00			1973	86213						
		1 50			1.000	0.500	CT	0.486	0.39	23.30			1973	86213						
		3 00			1.000	0.500	CT	0.490	0.32	21.30			1973	86213						
		3 00			1.000	0.498	CT	0.491	0.32	21.30			1973	86213						
		1 50			1.000	0.500	CT	0.479	0.35	22.60			1973	86213						
		2 00			1.000	0.501	CT	0.474	0.29	20.50			1973	86213						
		1 75			1.000	0.499	CT	0.480	0.34	22.00			1973	86213						
		1 50			1.000	0.500	CT	0.490	0.38	23.90			1973	86213						
		2 00			1.000	0.501	CT	0.477	0.37	23.40			1973	86213						
		2 00			1.000	0.500	CT	0.479	0.39	23.70			1973	86213						
		1 75			1.000	0.501	CT	0.475	0.39	24.00			1973	86213						
		1 75			1.000	0.499	CT	0.471	0.40	24.50	22.8/	1.3	1973	86213						
T651 (417)	P	2 25	84	S-L	1.500	0.749	CT	0.757	0.37	24.40			1973	86213						
		2 25			1.500	0.749	CT	0.770	0.37	24.30			1973	86213						
		2 37			1.500	0.750	CT	0.782	0.29	22.00			1973	86213						
		2 37			1.500	0.749	CT	0.734	0.41	26.00			1973	86213						
		2 25			1.500	0.750	CT	0.739	0.29	22.30			1973	86213						

Table 7.9.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEMP (F)	THICK (IN)	SPECIMEN		K(1C)	CRACK LENGTH (IN)	CRACK LENGTH (IN)	K(1C)/TYB)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)					WIDTH (IN)	THICK (IN)								
1651 (417)	P	2.25	65.3	S-L	84	1.500	0.750	CT	0.799	0.31	23.00	23.7/	1.5	1973	86213	

Table 7.10.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 2219 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SORT(IN)) DEVIATION		(NUMBER OF SPECIMENS)	
	L-I	I-L	S-L	S-L
PLATE				
	T851	33.4 ± 2.3 (48)	29.7 ± 3.2 (78)	23.0 ± 2.4 (14)
	T87	28.0 ± 3.0 (6)	22.0 ± 0.4 (2)	-----
T87-300F 100HRS	34.8 ± 0.4 (2)	-----	-----	-----
<u>FORGING</u>				
CONDITION/HT	L-I	I-L	S-L	S-L
T851	-----	-----	25.6 ± 3.1 (85)	
T852	39.2 ± 3.2 (25)	27.1 ± 2.2 (24)	25.3 ± 3.1 (60)	

Table 7.10.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2219

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT: L.H.A.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
T851	PLATE	0.08	0.10		7.10
T851	PLATE	0.08	1.00	SPEC. THK=1.00"	7.60 94.0
T851	PLATE	0.08	1.00		8.48
T851	PLATE	0.08	6.00	SPEC. THK=1.00"	7.74 60.3
T851	PLATE	0.08	6.00		0.40 4.77
T851	PLATE	0.08	6.00	SPEC. THK=0.50"	3.52 26.5
T851	PLATE	0.08	6.00		3.95 24.4
T851	PLATE	0.08	63.30		0.28 4.67
T851	PLATE	0.30	6.00		0.90
T851	PLATE	0.50	6.00		0.72 8.15
T8511	EXTRUDED BAR	0.08	6.00		0.23 2.12
T8511	EXTRUDED BAR	0.30	6.00		6.44
T852	BILLET	0.08	6.00		2.35

Table 7.10.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2219

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT LAB AIR AT R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)					
					2	5	10	20	50	100
T851	PLATE	-1.00	1 00-20 00		5.92	52.3				
T851	PLATE	-1.00	6 00		6.81					
T851	PLATE	-0.50	5 20		6.89					
T851	PLATE	-0.30	6 00		6.88	52.5	3617			
T851	PLATE	-0.10	6 00		6.79	44.9	3707			
T851	PLATE	0.00	5 20		6.25	54.8				
T851	PLATE	0.00	6 00		4.33	34.6				
T851	PLATE	0.01	3 00			44.5	1622			
T851	PLATE	0.01	6 00			46.2	1788			
T851	PLATE	0.04	1 00-20 00		4.24					
T851	PLATE	0.05	1 00-20 00		2.46	33.9				
T851	PLATE	0.05	1 00-20 00		3.58					
T851	PLATE	0.05	1 00-20 00		5.14	48.3				
T851	PLATE	0.08	6 00		5.74					
T851	PLATE	0.10	1 00-20 00			44.9				
T851	PLATE	0.20	6 00			90.9				
T851	PLATE	0.30	6 00		0.69	7.86	76.3			
T851	PLATE	0.50	1 00-20 00			10.1				
T851	PLATE	0.60	1 00-20 00			12.2				
T851	PLATE	0.70	6 00		1.37	17.8	1173			

Table 7.10.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2219

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT S.T.W
A.T.R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)
				2.5 5 10 20 50 100	
T851	PLATE	0.08	0.10		55.6
T851	PLATE	0.08	1.00		7.14 64.0
T851	PLATE	0.08	1.00	0.60	
T851	PLATE	0.08	6.00		10.6 59.5
T851	PLATE	0.30	1.00		8.68 65.6
T851	PLATE	0.50	1.00		0.80 11.6
T8511	EXTRUDED BAR	0.08	1.00		7.39
T852	FORGING	0.33	20.00		6.28
T852	FORGING	0.33	20.00		10.2

Table 7.10.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2219

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: DRY AIR AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	2.5	5	10	20	50	100
T852	FORGING	0.33	2.00-20.00				7.08	4.60		
T852	FORGING	0.33	2.00-20.00				6.78			
T852	FORGING	0.33	40.00			0.363	3.97			

Table 7.10.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2219

TEST CONDITIONS

SPECIMEN ORIENTATION 1-L

ENVIRONMENT: L.H.A.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
T851	PLATE	0.08	6.00		5.43 33.3
T851	PLATE	0.08	6.00		8.71 100.
T8511	EXTRUDED BAR	0.08	6.00		4.26

Table 7.10.1.1.7

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINIUM 2219

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT: H.H.A.
AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ. (HZ)	DELTA K LEVELS: (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
T852	FORGING	0.33	2.00-20.00		8.32
T852	FORGING	0.33	2.00-20.00		13.0

Table 7.10.1.8

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 2219

TEST CONDITIONS

SPECIMEN ORIENTATION T-I

ENVIRONMENT S T W
A T R T

CONDITION/HT	PRODUCT FIRM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
				FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)						
T851	PLATE	0.08	1.00		1.02	10.8	81.5			
T8511	EXTRUDED BAR	0.08	1.00		0.64	7.37				
T852	FORGING	0.33	2.00-20.00				9.83	204		
T852	FORGING	0.33	2.00-20.00				16.5			
T852	FORGING	0.33	20.00				10.3			

Table 7.10.2.1

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN		CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV (KSI*SQRT IN)	DATE	REFER	
	FORM	THICK (IN)		THICK (IN)	DESIGN (IN)							
T851	P	3.00	50.0	8.000	2.000	CT	1.22	35.00		1974	90011	
		3.00	50.1	5.044	1.503	CT	1.29	36.50		1978	MPC01	
		3.00	50.1	6.016	1.998	CT	2.623	37.10		1978	MPC01	
		3.00	50.1	50.1	4.019	1.999	CT	1.36	36.90		1978	MPC01
		3.00	50.1	50.1	6.000	1.999	CT	1.33	36.90		1973	86213
		3.00	50.1	50.1	5.010	1.987	CT	1.45	38.10		1973	86213
		3.00	50.1	50.1	5.010	1.987	CT	1.28	35.90		1973	86213
		3.00	50.1	50.1	4.000	1.999	CT	1.33	36.50		1973	86213
		3.00	50.1	50.1	4.000	1.999	CT	1.28	35.90		1973	86213
		3.00	50.1	50.1	4.000	1.998	CT	1.28	35.80		1973	86213
		3.00	50.1	50.1	5.010	2.000	CT	1.28	35.90		1973	86213
		1.37	1.37	51.0	2.982	1.374	CT	0.93	31.30		1978	MPC01
		1.37	1.37	51.0	2.977	1.374	CT	0.93	31.30		1978	MPC01
		1.37	1.37	51.0	3.000	1.420	NB	0.93	34.80		1973	86213
		1.37	1.37	51.0	3.000	1.420	NB	1.16	34.80		1973	86213
		1.37	1.37	51.0	3.000	1.420	NB	1.40	38.10		1973	86213
		1.37	1.37	51.0	2.978	1.374	CT	1.14	34.50		1973	86213
		2.62	2.62	51.6	3.027	1.500	CT	0.87	30.40		1978	MPC01
		2.62	2.62	51.6	3.004	1.500	CT	0.87	30.90		1978	MPC01
		3.25	3.25	51.7	4.989	1.750	CT	0.87	30.40		1978	MPC01
		1.37	1.37	52.0	3.022	1.376	CT	1.12	34.90		1978	MPC01
		3.00	3.00	52.0	5.000	1.498	CT	0.87	30.70		1978	MPC01
		1.37	1.37	52.0	2.975	1.376	CT	1.20	36.00		1973	86213
		3.00	3.00	52.0	5.000	1.498	CT	0.90	31.20		1978	MPC01
		3.00	3.00	52.4	3.026	1.499	CT	1.08	34.20		1973	86213
		2.90	2.90	52.4	3.022	1.500	CT	0.99	33.20		1978	MPC01
		3.00	3.00	52.4	2.996	1.499	CT	0.96	32.80		1978	MPC01
		3.00	3.00	52.5	2.987	1.499	CT	0.96	32.80		1978	MPC01
		3.00	3.00	52.5	2.977	1.499	CT	1.02	33.80		1978	MPC01
		2.90	2.90	52.5	4.973	2.000	CT	1.02	33.80		1978	MPC01
		2.90	2.90	52.5	4.987	2.503	CT	0.99	33.40		1978	MPC01
		1.75	1.75	52.6	4.962	1.751	CT	1.02	33.60		1978	MPC01
		2.90	2.90	52.8	4.987	2.001	CT	0.84	30.80		1978	MPC01
	2.90	2.90	53.0	3.027	1.503	CT	0.90	31.80		1978	MPC01	
	2.90	2.90	53.0	5.045	2.000	CT	0.81	30.70		1978	MPC01	
	3.00	3.00	53.4	5.010	1.997	CT	0.90	32.20		1978	MPC01	
	2.90	2.90	53.5	4.965	2.002	CT	0.87	31.50		1973	86213	
	2.90	2.90	53.5	4.967	2.501	CT	0.87	31.60		1978	MPC01	
	2.90	2.90	53.5	5.018	2.002	CT	0.93	32.90		1978	MPC01	
	2.90	2.90	53.6	4.954	2.002	CT	0.90	32.20		1978	MPC01	
							0.96	33.60				

Table 7.10.2.1 (Con't.)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN		DESIGN	CRACK LENGTH (IN)	K(1C)	2.9* (IN)	K(1C)/TYS)**2	K(1C) MEAN (KSI*SORT IN)	STAN DEV	DATE	REFER		
	FORM	THICK (IN)		THICK (IN)	WIDTH (IN)											
T851	P	2.90	R.T.	L-T	53.6	4.989	2.501	CT	2.644	0.99	33.80		1978	MPC01		
		3.00			53.7	4.010	1.998	CT	2.043	0.79	30.10		1973	86213		
		1.00			53.8	1.990	0.965	CT	1.035	0.81	30.90		1978	MPC01		
		1.00			53.8	2.016	0.965	CT	1.008	0.78	30.60		1978	MPC01		
		1.00			53.8	1.990	0.965	CT	1.015	0.78	30.60		1978	MPC01		
		3.00			54.0	8.000	1.996	CT	3.991	1.03	34.70		1973	85836		
		2.90			54.3	4.969	2.002	CT	2.584	0.81	31.20		1978	MPC01		
		2.90			54.3	5.006	2.501	CT	2.703	0.81	31.00		1978	MPC01		
		2.50			55.7	4.968	1.753	CT	2.633	0.96	34.60	33.4/	2.3		1978	MPC01
		1.37	- 112	T-L	55.0	3.000	1.405	NB	1.612	1.00	34.70				1973	86213
		T851	P	1.37	R.T.	T-L	46.2	3.000	1.402	NB	1.524	1.10	32.60		1973	86213
				1.37			47.4	1.994	1.000	CT	1.017	0.93	29.20		1978	MPC01
				1.75			48.0	3.000	1.508	CT	1.611	1.28	34.40		1972	84306
				1.75			48.0	5.000	1.504	CT	2.615	1.48	37.00		1972	84306
				1.75			48.0	5.000	1.504	CT	2.609	1.48	37.00		1972	84306
1.75					48.0	2.990	1.508	CT	1.573	1.24	33.90		1972	84306		
1.37					49.2	2.985	1.405	NB	1.582	0.81	28.20		1978	MPC01		
1.37					49.2	3.016	1.402	NB	1.538	0.99	31.10		1978	MPC01		
1.37					49.2	2.974	1.402	NB	1.487	0.99	31.30		1978	MPC01		
1.37					49.2	2.974	1.405	NB	1.487	0.84	28.70		1978	MPC01		
1.37					49.2	3.000	1.403	NB	1.526	1.09	32.50		1973	86213		
1.37					49.2	3.008	1.403	NB	1.534	1.08	32.80		1978	MPC01		
1.37					49.2	2.991	1.402	NB	1.585	1.08	32.80		1978	MPC01		
1.37					49.2	3.000	1.405	NB	1.535	0.94	30.20		1973	86213		
3.25					49.2	4.977	1.750	CT	2.638	0.84	28.90		1978	MPC01		
1.37			49.2	3.000	1.405	NB	1.634	0.92	29.90		1973	86213				
1.37			49.2	3.000	1.402	NB	1.584	1.10	32.70		1973	86213				
1.37			49.2	3.000	1.402	NB	1.605	1.16	33.90		1973	86213				
1.37			49.3	2.973	1.000	CT	1.546	0.90	29.70		1978	MPC01				
1.38			49.3	3.000	1.380	CT	1.538	0.88	29.30		1972	82880				
1.37			49.3	2.990	1.000	CT	1.555	0.96	30.80		1978	MPC01				
1.37			49.3	3.002	1.000	CT	1.561	0.90	29.80		1978	MPC01				
1.37			49.3	2.000	0.875	CT	1.020	0.81	28.30		1978	MPC01				
1.37			49.3	2.014	0.875	CT	1.007	0.78	27.90		1978	MPC01				
1.37			49.3	2.975	1.125	CT	1.547	0.87	29.50		1978	MPC01				
1.38			49.3	2.000	1.000	CT	1.057	0.79	27.70		1972	82880				
1.37			49.3	3.025	1.125	CT	1.573	0.87	29.30		1978	MPC01				

Table 7.10.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	R	T	L	THICK (IN)	FORM	PRODUCT-- (IN)	SPECIMEN		DESIGN	K (IC)	CRACK LENGTH (IN)	2.5* (K(IC)/TVS)**2 (IN)	K (IC) (KSI*SQRT IN)	K (IC) MEAN DEV (KSI*SQRT IN)	STAN DEV	DATE	REFER
	W	B																			
T851	P	1.38	49.3	T-L				2.000	1.000	CT	1.082	0.77	27.40	1972	B2880						
		1.38	49.3					3.000	1.380	CT	1.557	0.86	28.90	1972	B2880						
		1.37	49.3					2.012	0.875	CT	1.026	0.84	28.70	1978	MPC01						
		3.00	49.3					4.000	2.001	CT	2.077	1.07	32.30	1973	B6213						
		1.38	49.3					3.000	1.380	CT	1.555	0.86	28.90	1972	B2880						
		1.37	49.3					1.494	0.750	CT	0.792	0.67	25.80	1978	MPC01						
		1.37	49.3					3.006	1.125	CT	1.563	0.90	29.70	1978	MPC01						
		1.38	49.3					2.000	1.000	CT	1.069	0.77	27.40	1972	B2880						
		3.00	49.3					4.000	1.999	CT	2.085	1.05	32.00	1973	B6213						
		1.37	49.7					2.004	1.000	CT	1.042	0.75	27.40	1978	MPC01						
		1.37	49.7					2.010	1.000	CT	1.045	0.84	29.10	1978	MPC01						
		1.37	49.7					2.004	0.999	CT	1.042	0.81	28.60	1978	MPC01						
		2.00	50.0					3.000	1.500	CT	---	1.30	36.00	1974	90011						
		3.00	50.0					5.000	2.000	CT	---	1.15	34.00	1974	90011						
		2.00	50.1					4.959	1.750	CT	---	1.15	34.00	1974	90011						
		3.00	50.6					3.000	1.498	CT	2.628	0.81	28.80	1978	MPC01						
		3.00	50.6					5.000	1.497	CT	1.550	0.72	27.20	1973	B6213						
		3.00	50.6					3.000	1.497	CT	2.582	0.82	28.90	1973	B6213						
		3.00	50.6					3.000	1.498	CT	1.550	0.71	26.90	1973	B6213						
		1.37	50.8					3.026	1.375	CT	2.575	0.80	28.60	1973	B6213						
		1.37	50.8					3.000	1.497	CT	1.543	0.78	28.80	1978	MPC01						
		1.37	50.8					3.000	1.420	NB	1.500	0.81	29.00	1978	MPC01						
		1.37	50.8					2.980	1.420	NB	1.520	0.93	31.40	1978	MPC01						
		1.37	50.8					2.981	1.420	NB	1.550	1.29	36.60	1978	MPC01						
		1.37	50.8					2.973	1.375	CT	1.546	0.72	27.50	1978	MPC01						
		1.37	50.8					3.000	1.420	NB	1.560	1.05	33.30	1978	MPC01						
		1.00	51.2					1.993	0.965	CT	1.096	0.75	28.40	1978	MPC01						
		1.00	51.2					2.013	0.963	CT	1.067	0.78	28.90	1978	MPC01						
		1.00	51.2					1.986	0.964	CT	1.013	0.72	28.00	1978	MPC01						
		2.90	51.6					2.991	1.249	CT	1.645	0.78	29.40	1978	MPC01						
		2.90	51.8					4.993	2.501	CT	2.696	0.70	27.90	1978	MPC01						
		2.90	51.8					4.975	2.002	CT	2.587	0.62	26.20	1978	MPC01						
		2.90	51.9					3.030	1.504	CT	1.697	0.65	26.80	1978	MPC01						
		2.90	51.9					4.996	2.002	CT	2.609	0.70	27.60	1978	MPC01						
		2.90	52.0					4.996	2.002	CT	2.598	0.72	28.20	1978	MPC01						
		2.90	52.0					5.033	2.002	CT	2.617	0.65	27.00	1978	MPC01						
		2.90	52.0					5.013	2.501	CT	2.657	0.70	28.00	1978	MPC01						
		---	52.0					7.990	1.992	CT	4.067	1.05	33.70	1973	B5836						
		2.90	52.2					5.008	2.002	CT	2.604	0.75	28.90	1978	MPC01						

Table 7.10.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	THICK (IN)	TEMP (F)	SPECIMEN		DESIGN	CRACK LENGTH (IN)	K(1C) (KSI#SORT IN)	K(1C) MEAN DEV (IN)	STAN DEV	DATE	REFER	
	FORM	THICK (IN)					WIDTH (IN)	THICK (IN)								2.5*
T851	P	2.90	53.6	L-T	4.989	R.T.	2.501	CT	2.644	33.80	0.99	33.80		1978	MPC01	
		3.00	53.7		4.010		1.998	CT	2.043	30.10	0.79	30.10		1973	86213	
		1.00	53.8		1.990		0.965	CT	1.039	30.90	0.81	30.90		1978	MPC01	
		1.00	53.8		2.016		0.965	CT	1.008	30.60	0.78	30.60		1978	MPC01	
		1.00	53.8		1.990		0.965	CT	1.015	30.60	0.78	30.60		1978	MPC01	
		3.00	54.0		8.000		1.996	CT	3.991	34.70	1.03	34.70		1973	85836	
		2.90	54.3		4.969		2.002	CT	2.984	31.20	0.81	31.20		1978	MPC01	
		2.90	54.3		5.006		2.501	CT	2.703	31.00	0.81	31.00		1978	MPC01	
		2.50	55.7		4.968		1.753	CT	2.633	34.60	0.96	34.60	33.4/	2.3	1978	MPC01
		1.37	55.0		3.000		1.405	NB	1.612	34.70	1.00	34.70		1973	86213	
T851	P	1.37	46.2	T-L	3.000	R.T.	1.402	NB	1.524	32.60	1.10	32.60		1973	86213	
		1.37	47.4		1.994		1.000	CT	1.017	29.20	0.93	29.20		1978	MPC01	
		1.75	48.0		3.000		1.508	CT	1.611	34.40	1.28	34.40		1972	84306	
		1.75	48.0		5.000		1.504	CT	2.615	37.00	1.48	37.00		1972	84306	
		1.75	48.0		5.000		1.508	CT	2.609	37.00	1.48	37.00		1972	84306	
		1.37	49.2		2.985		1.405	NB	1.582	28.20	0.81	28.20		1978	MPC01	
		1.37	49.2		3.016		1.402	NB	1.538	31.10	0.99	31.10		1978	MPC01	
		1.37	49.2		2.974		1.402	NB	1.487	28.70	0.84	28.70		1978	MPC01	
		1.37	49.2		3.000		1.403	NB	1.526	32.50	1.09	32.50		1973	86213	
		1.37	49.2		3.008		1.403	NB	1.534	32.80	1.08	32.80		1978	MPC01	
		1.37	49.2		2.991		1.402	NB	1.989	30.20	0.94	30.20		1973	86213	
		3.25	49.2		3.000		1.405	NB	1.535	28.90	0.84	28.90		1978	MPC01	
		1.37	49.2		4.977		1.750	CT	2.638	29.70	0.92	29.70		1973	86213	
		1.37	49.2		3.000		1.402	NB	1.584	32.70	1.10	32.70		1973	86213	
		1.37	49.2		3.000		1.402	NB	1.605	33.50	1.16	33.50		1973	86213	
		1.37	49.3		2.973		1.000	CT	1.546	29.70	0.90	29.70		1978	MPC01	
		1.38	49.3		3.000		1.380	CT	1.538	29.30	0.88	29.30		1972	82880	
		1.37	49.3		2.990		1.000	CT	1.555	30.80	0.96	30.80		1978	MPC01	
		1.37	49.3		3.002		1.000	CT	1.561	29.80	0.90	29.80		1978	MPC01	
		1.37	49.3		2.000		0.875	CT	1.020	28.30	0.81	28.30		1978	MPC01	
		1.37	49.3		2.014		0.875	CT	1.007	27.90	0.78	27.90		1978	MPC01	
		1.37	49.3		2.975		1.125	CT	1.547	29.50	0.87	29.50		1978	MPC01	
		1.38	49.3		2.000		1.000	CT	1.057	27.70	0.79	27.70		1972	82880	
		1.37	49.3		3.025		1.125	CT	1.573	29.30	0.87	29.30		1978	MPC01	

Table 7.10.2.1 (Cont'd)

CONDITION	ALUMINUM	2219	K(1C)	K(1C)	YIELD STRENGTH (KSI)	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER
T851	P	1.37	88	S-L	52.3	1.000	0.500	CT	0.496	0.39	0.39	20.60	21.2/	1.0	1973	86213	
T851	F	---	R T	L-S	41.9	3.001	1.501	CT	1.563	1.16	1.16	28.98				1976	MD001
					41.9	3.001	1.499	CT	1.542	1.16	1.16	28.64				1976	MD001
					46.1	3.003	1.500	CT	1.566	1.02	1.02	29.59				1976	MD001
					46.4	3.001	1.500	CT	1.580	1.15	1.15	31.58				1976	MD001
					46.4	3.003	1.499	CT	1.569	1.08	1.08	30.60				1976	MD001
					50.1	3.005	1.500	CT	1.418	1.13	1.13	33.71				1976	MD001
					50.1	3.003	1.500	CT	1.444	1.18	1.18	34.55				1976	MD001
					50.9	1.998	1.001	CT	0.995	0.57	0.57	24.49	30.3/	3.0	1976	MD001	
T851	F	---	R T	T-S	45.2	2.997	1.495	CT	1.589	0.64	0.64	22.91				1977	MD001
					47.5	1.998	1.001	CT	1.000	0.63	0.63	23.96				1976	MD001
					47.5	3.001	1.502	CT	1.619	0.50	0.50	21.42				1976	MD001
					47.7	1.999	1.000	CT	1.003	0.71	0.71	25.90				1976	MD001
					47.9	2.998	1.502	CT	1.607	0.92	0.92	29.13				1977	MD001
					48.1	2.000	1.001	CT	1.059	0.73	0.73	26.01				1977	MD001
					48.1	2.996	1.496	CT	1.615	0.79	0.79	27.04				1977	MD001
					48.2	3.001	1.501	CT	1.555	0.51	0.51	21.78				1976	MD001
					48.3	3.001	1.501	CT	1.531	0.67	0.67	25.13				1976	MD001
					48.4	3.000	1.501	CT	1.621	0.52	0.52	22.14				1976	MD001
					48.5	1.998	1.001	CT	1.047	0.86	0.86	28.90				1976	MD001
					48.7	1.995	1.001	CT	1.033	0.75	0.75	26.67				1976	MD001
					49.0	2.997	1.495	CT	1.996	0.64	0.64	24.84				1977	MD001
					49.2	1.996	1.001	CT	0.997	0.66	0.66	23.29				1976	MD001
					49.2	1.997	1.000	CT	1.031	0.56	0.56	23.35				1976	MD001
					50.1	1.999	0.997	CT	1.033	0.69	0.69	26.35				1977	MD001
					50.4	3.000	1.501	CT	1.562	0.76	0.76	27.86				1976	MD001
					51.9	3.000	1.501	CT	1.563	0.71	0.71	27.77	25.3/	2.3	1976	MD001	
T851	F	---	R T	S-L	46.2	2.997	1.495	CT	1.643	0.67	0.67	24.00				1977	MD001
					46.2	2.996	1.495	CT	1.661	0.67	0.67	24.08				1977	MD001
					46.2	2.996	1.496	CT	1.616	0.68	0.68	24.13				1977	MD001
					46.8	3.003	1.502	CT	1.614	0.61	0.61	22.84				1977	MD001
					46.8	3.003	1.502	CT	1.556	0.62	0.62	23.40				1976	MD001
					46.8	3.001	1.501	CT	1.567	0.62	0.62	23.47				1976	MD001
					47.1	3.007	1.504	CT	1.700	0.69	0.69	24.75				1979	MD001
					47.7	1.999	1.001	CT	1.047	0.65	0.65	24.45				1977	MD001

Table 7.10.2.1 (Con't)

CONDITION	--PRODUCT-- FORM (IN)	TEST SPECIMEN ORIENT (F)	YIELD STRENGTH (KSI)	ALUMINUM		2219		K(1C)		2.5* (IN)	K(1C)/TYS)**2 (KSI*SQRT IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER
				W	B	W	B	A							
T851	F	---	47.7	1.998	1.001	CT	CT	1.070	0.67	24.72	1977	MD001			
		---	47.8	3.001	1.501	CT	CT	1.542	0.52	21.89	1976	MD001			
		---	47.9	2.997	1.501	CT	CT	1.532	0.64	24.27	1976	MD001			
		---	48.6	2.999	1.502	CT	CT	1.584	0.80	27.12	1977	MD001			
		---	48.7	1.997	1.001	CT	CT	1.617	0.77	27.14	1977	MD001			
		---	49.0	1.997	1.001	CT	CT	1.083	0.52	22.29	1976	MD001			
		---	49.0	1.998	1.001	CT	CT	1.026	0.74	26.83	1976	MD001			
		---	49.1	3.001	1.499	CT	CT	1.040	0.69	25.79	1976	MD001			
		---	49.1	1.998	1.000	CT	CT	1.575	0.77	27.41	1977	MD001			
		---	49.1	1.998	1.000	CT	CT	1.038	0.60	24.23	1976	MD001			
		---	49.1	1.998	1.000	CT	CT	1.039	0.63	24.70	1976	MD001			
		---	49.1	2.999	1.502	CT	CT	1.552	1.19	33.88	1977	MD001			
		---	49.1	1.998	1.001	CT	CT	1.050	0.58	23.79	1976	MD001			
		---	49.1	2.000	1.001	CT	CT	1.080	0.74	26.73	1977	MD001			
		---	49.1	1.998	0.999	CT	CT	1.033	0.64	24.89	1976	MD001			
		---	49.1	3.001	1.501	CT	CT	1.586	0.58	23.84	1976	MD001			
		---	49.1	3.003	1.501	CT	CT	1.572	0.62	24.90	1976	MD001			
		---	49.1	1.997	1.000	CT	CT	1.057	0.64	25.00	1976	MD001			
		---	49.1	1.998	1.000	CT	CT	1.035	0.62	24.51	1976	MD001			
		---	49.1	3.001	1.502	CT	CT	1.531	0.82	28.16	1977	MD001			
		---	49.1	3.000	1.500	CT	CT	1.636	0.58	23.85	1977	MD001			
		---	49.1	1.998	1.001	CT	CT	1.044	0.68	25.64	1977	MD001			
		---	49.2	2.999	1.502	CT	CT	1.602	0.46	21.19	1976	MD001			
		---	49.2	3.003	1.501	CT	CT	1.608	0.45	20.97	1976	MD001			
		---	49.3	2.997	1.496	CT	CT	1.592	0.92	29.96	1977	MD001			
		---	49.3	2.996	1.496	CT	CT	1.633	0.83	28.54	1977	MD001			
		---	49.4	3.007	1.502	CT	CT	1.516	0.94	30.42	1977	MD001			
		---	49.5	3.001	1.501	CT	CT	1.535	0.58	24.00	1976	MD001			
		---	49.5	3.002	1.500	CT	CT	1.528	0.77	27.60	1976	MD001			
		---	49.7	2.999	1.500	CT	CT	1.595	0.80	28.16	1977	MD001			
		---	49.7	3.000	1.500	CT	CT	1.634	0.79	28.03	1977	MD001			
		---	49.7	3.000	1.504	CT	CT	1.641	0.57	23.89	1978	MD001			
		---	49.7	3.000	1.499	CT	CT	1.626	0.82	28.62	1977	MD001			
		---	49.7	3.000	1.501	CT	CT	1.586	0.63	25.12	1978	MD001			
		---	49.8	1.996	1.001	CT	CT	1.010	0.38	19.50	1976	MD001			
		---	49.8	1.996	1.001	CT	CT	1.040	0.43	20.75	1976	MD001			
		---	49.9	1.996	1.002	CT	CT	1.071	0.71	26.69	1976	MD001			
		---	49.9	2.000	1.001	CT	CT	1.053	0.51	22.66	1977	MD001			
		---	49.9	1.997	1.002	CT	CT	1.065	0.66	25.79	1976	MD001			

Table 7.10.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	SPECIMEN		DESIGN	CRACK LENGTH (IN)	K(1C)	2.5* (IN)	K(1C)/TYS)**2 (IN)	K(1C) MEAN (IN)	STAN DEV (IN)	DATE	REFER				
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)										A	B	W	H
T852	F	7.50	43.4	L-S	R.T.	1.499	1.499	CT	1.539	0.89	25.92	1977	MD001							
									1.507	0.91	26.22	1977	MD001							
									1.548	1.14	32.82	1976	MD001							
									2.580	1.72	34.80	1977	AL001							
									2.550	1.55	33.00	1977	AL001							
									2.570	1.79	35.50	1977	AL001							
									2.560	1.98	38.60	1977	AL001							
									2.520	1.91	39.00	1977	AL001							
									2.550	2.08	40.70	1977	AL001							
									2.520	1.81	38.00	1977	AL001							
T852	F	7.50	41.9	L-T	R.T.	2.500	2.500	CT	2.580	1.72	34.80	1977	AL001							
									2.550	1.55	33.00	1977	AL001							
									2.570	1.79	35.50	1977	AL001							
									2.560	1.98	38.60	1977	AL001							
									2.520	1.91	39.00	1977	AL001							
									2.550	2.08	40.70	1977	AL001							
									2.520	1.81	38.00	1977	AL001							
									2.580	1.68	37.00	1977	AL001							
									2.560	1.63	36.90	1977	AL001							
									2.530	1.83	42.10	1977	AL001							
T852	F	3.00	53.0	L-T	82	1.502	1.502	CT	2.055	0.99	33.30	1973	86213							
									1.985	1.41	34.60	1973	86213							
									1.970	1.27	35.20	1973	86213							
									1.978	1.20	35.50	1973	86213							
									1.617	1.06	28.53	1976	MD001							
									1.569	0.81	26.04	1976	MD001							
									1.566	1.30	34.08	1976	MD001							
									1.978	1.20	35.50	1973	86213							
									1.978	1.20	35.50	1973	86213							
									1.978	1.20	35.50	1973	86213							
T852	F	6.75	46.0	L-T	85	1.998	1.998	CT	1.985	1.41	34.60	1973	86213							
									1.970	1.27	35.20	1973	86213							
									1.978	1.20	35.50	1973	86213							
T852	F	6.75	49.4	T-S	R.T.	1.502	1.502	CT	1.617	1.06	28.53	1976	MD001							
									1.569	0.81	26.04	1976	MD001							
									1.566	1.30	34.08	1976	MD001							

Table 7.10.2.1 (Con't)

CONDITION	---PRODUCT--- FORM THICK (IN)		TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM 2219		SPECIMEN THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* K(KIC)/TYS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	W	B				A	K(KIC)								
T852	F	---	R. T.	T-S	47.2	3.000	1.500	CT	1.574	1.12	31.70	1976 MD001			
		---			47.8	3.000	1.502	CT	1.562	0.77	26.66	1976 MD001			
		---			47.9	2.999	1.501	CT	1.578	0.81	27.33	1976 MD001			
		---			48.0	3.000	1.502	CT	1.549	0.91	29.10	1976 MD001	29.1/	2.9	
T852	F	5.50	R. T.	T-L	43.1	5.000	2.500	CT	2.620	1.07	28.20	1977 AL001			
		5.50			43.1	5.000	2.500	CT	2.570	1.10	28.60	1977 AL001			
		---			44.0	5.000	1.984	CT	2.502	0.75	24.10	1973 85836			
		---			44.0	5.000	1.998	CT	2.271	0.63	22.20	1973 85836			
		7.50			44.2	3.000	1.500	CT	1.540	0.81	25.10	1977 AL001			
		7.50			44.2	3.000	1.500	CT	1.530	0.69	23.30	1977 AL001			
		4.50			45.7	5.000	2.500	CT	2.540	0.95	28.10	1977 AL001			
		4.50			45.7	5.000	2.500	CT	2.530	0.97	28.40	1977 AL001			
		5.50			46.4	5.000	2.500	CT	2.520	0.74	25.20	1977 AL001			
		3.50			49.8	5.000	2.500	CT	2.580	0.80	28.20	1977 AL001			
		3.50			49.8	5.000	2.500	CT	2.560	0.83	28.70	1977 AL001			
		3.50			49.8	5.000	2.500	CT	2.560	0.80	28.10	1977 AL001			
		2.50			49.9	5.000	2.490	CT	2.570	0.68	26.00	1977 AL001			
		2.50			49.9	5.000	2.500	CT	2.560	0.94	30.60	1977 AL001			
		2.50			49.9	5.000	2.490	CT	2.510	0.68	26.10	1977 AL001			
		3.50			50.2	5.000	2.500	CT	2.530	0.68	26.20	1977 AL001			
		3.50			50.2	5.000	2.500	CT	2.520	0.67	26.00	1977 AL001			
		3.50			50.2	5.000	2.500	CT	2.500	0.62	24.90	1977 AL001			
		2.00			50.6	3.000	1.500	CT	1.510	0.84	29.40	1977 AL001			
		4.50			50.6	5.000	2.500	CT	2.570	0.83	29.10	1977 AL001			
		2.00			50.6	3.000	1.500	CT	1.560	0.79	28.50	1977 AL001			
		2.00			50.6	3.000	1.500	CT	1.560	0.83	29.20	1977 AL001			
		4.50			50.6	5.000	2.500	CT	2.510	0.87	29.80	1977 AL001			
		4.50			50.6	5.000	2.500	CT	2.510	0.74	27.50	1977 AL001	27.1/	2.2	
T852	F	3.00	82	T-L	53.3	4.000	1.501	CT	2.037	0.43	22.00	1973 86213			
T852	F	3.50	84	T-L	48.0	3.990	1.686	CT	2.077	0.87	28.30	1973 86213			
T852	F	6.75	85	T-L	46.2	3.990	1.997	CT	2.067	0.89	27.50	1973 86213			
		6.75			46.5	3.990	1.997	CT	2.127	0.95	28.70	1973 86213			
		6.75			49.2	4.000	1.997	CT	2.080	0.56	23.30	1973 86213			
		6.75			49.7	3.990	1.997	CT	1.987	0.62	24.70	1973 86213			
		6.75			49.7	4.000	1.997	CT	2.019	0.51	22.50	1973 86213	25.3/	2.7	

Table 7.10.2.1 (Con't)

CONDITION	---PRODUCT--- FORM	THICK (IN)	TEST TEMP (F)	TEST SPECIMEN ORIENT	YIELD STRENGTH (KBI)	ALUMINUM		SPECIMEN		CRACK LENGTH (IN)	K(1C)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
						WIDTH (IN)	THICK (IN)	DESIGN	DESIGN							
						U	B	A								
T852	F	---	R T.	S-T	43.0	3.000	1.502	CT	1.565	1.20	29.88	1976	MD001			
		---			44.7	2.999	1.501	CT	1.564	0.98	28.00	1976	MD001			
		---			45.2	2.999	1.500	CT	1.562	0.82	25.89	1976	MD001			
		---			48.8	3.000	1.502	CT	1.573	0.76	26.97	1976	MD001			
		---			49.1	3.000	1.501	CT	1.546	1.03	31.64	28.5/ 2.3	1976	MD001		
T852	F	3.00	82	S-T	52.7	2.500	0.748	CT	1.244	0.46	22.60	1973	86213			
T852	F	3.50	84	S-T	50.0	2.900	1.000	CT	1.231	0.73	27.10	1973	86213			
T852	F	6.75	85	S-T	44.9	2.500	1.249	CT	1.233	0.67	23.30	1973	86213			
		6.75			46.7	2.900	1.249	CT	1.234	0.62	23.30	1973	86213			
		6.75			46.7	2.500	1.249	CT	1.243	0.69	24.60	1973	86213			
		6.75			48.7	2.500	0.998	CT	1.247	0.60	23.80	1973	86213			
		6.75			49.7	2.500	0.998	CT	1.185	0.51	22.50	23.5/ 0.8	1973	86213		
T852	F	---	R T.	S-L	42.6	3.000	1.500	CT	1.594	0.59	20.72	1977	MD001			
		---			42.9	1.997	0.999	CT	1.077	0.72	23.09	1976	MD001			
		---			42.9	1.997	0.999	CT	1.047	0.69	22.65	1976	MD001			
		---			43.2	3.001	1.502	CT	1.632	0.92	26.28	1977	MD001			
		---			43.2	3.001	1.501	CT	1.666	0.77	24.02	1977	MD001			
		---			43.6	1.999	0.999	CT	1.077	0.67	22.73	1976	MD001			
		---			44.0	3.009	1.500	CT	1.570	0.66	22.66	1976	MD001			
		---			44.0	3.001	1.501	CT	1.586	0.69	22.46	1976	MD001			
		---			44.0	3.009	1.502	CT	1.586	0.68	22.96	1976	MD001			
		---			44.0	2.998	1.500	CT	1.596	0.88	26.25	1976	MD001			
		---			44.0	2.999	1.500	CT	1.570	0.83	25.39	1976	MD001			
		7.50	---			44.1	4.000	2.000	CT	2.050	0.88	26.10	1977	AL001		
		7.50	---			44.1	4.000	2.000	CT	2.020	0.87	26.00	1977	AL001		
		---				44.2	2.999	1.500	CT	1.614	0.88	26.37	1976	MD001		
		---				44.2	3.000	1.500	CT	1.590	0.81	30.73	1976	MD001		
		---				44.2	2.999	1.500	CT	1.598	0.81	25.17	1976	MD001		
		---				44.2	3.000	1.502	CT	1.568	0.91	26.71	1976	MD001		
		---				44.2	3.000	1.499	CT	1.594	1.36	32.71	1976	MD001		
		---				44.2	3.000	1.502	CT	1.566	0.90	26.65	1976	MD001		
		---				44.2	3.000	1.500	CT	1.603	1.41	33.20	1976	MD001		
	---				44.2	3.000	1.500	CT	1.572	1.19	30.55	1976	MD001			
	---				44.5	3.001	1.499	CT	1.597	0.54	20.84	1976	MD001			
	---				44.5	3.005	1.501	CT	1.586	0.62	22.32	1976	MD001			

Table 7.10.2.1 (Con't)

CONDITION	---PRODUCT--- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* (IN)	K(1C)/TVS)**2 (KSI*SQRT IN)	K(1C) MEAN DEV (IN)	K(1C) STAN DEV	DATE	REFER
						2219	K(1C)										
T852	F	---	R. T.	S-L	44.5	3.001	1.502	CT	1.468	1.07	29.23	1976	MD001				
		---			44.5	3.000	1.500	CT	1.591	0.62	22.23	1976	MD001				
		---			44.5	3.007	1.501	CT	1.607	0.60	21.91	1976	MD001				
		---			44.7	1.998	0.999	CT	1.079	0.64	22.75	1976	MD001				
		---			45.3	1.997	0.998	CT	1.097	0.68	23.66	1976	MD001				
		---			45.4	3.000	1.501	CT	1.571	1.01	28.90	1976	MD001				
		---			45.4	3.001	1.501	CT	1.582	0.95	28.07	1976	MD001				
		---			45.6	3.001	1.501	CT	1.478	1.01	28.99	1976	MD001				
		---			46.7	2.996	1.502	CT	1.486	1.43	33.32	1977	MD001				
		---			46.8	1.995	1.000	CT	1.063	0.63	23.61	1976	MD001				
		4.50			47.0	3.000	1.500	CT	1.510	0.56	22.20	1977	AL001				
		4.50			47.0	3.000	1.500	CT	1.550	0.67	24.40	1977	AL001				
		5.50			47.2	2.000	1.000	CT	1.530	0.67	24.30	1977	AL001				
		---			47.2	3.001	1.502	CT	1.514	0.90	28.45	1976	MD001				
		5.50			47.2	2.000	1.000	CT	1.030	0.63	23.60	1977	AL001				
		---			48.9	1.997	0.999	CT	1.051	0.58	23.67	1976	MD001				
		---			49.1	3.000	1.501	CT	1.616	0.67	25.44	1977	MD001				
		---			49.3	3.003	1.501	CT	1.586	0.81	28.09	1976	MD001				
		---			49.6	3.003	1.502	CT	1.628	0.54	23.07	1977	MD001				
		3.50			49.7	2.000	1.000	CT	1.030	0.65	25.30	1977	AL001				
		3.50			49.7	2.000	1.000	CT	1.020	0.67	25.80	1977	AL001				
		3.50			49.7	2.000	1.000	CT	1.040	0.64	25.10	1977	AL001				
		5.50			50.8	4.000	2.000	CT	2.040	0.60	24.90	1977	AL001				
		5.50			50.8	4.000	2.000	CT	2.050	0.69	26.60	1977	AL001				
		5.50			50.8	4.000	2.000	CT	2.040	0.59	24.70	1977	AL001				
		3.50			51.1	2.000	1.000	CT	1.040	0.62	25.90	1977	AL001				
		2.50			51.1	2.000	1.000	CT	1.010	0.44	21.40	1977	AL001				
		2.50			51.1	2.000	1.000	CT	1.010	0.43	21.20	1977	AL001				
		2.50			51.1	2.000	1.000	CT	1.010	0.49	22.60	1977	AL001				
		3.50			51.1	2.000	1.000	CT	1.020	0.61	25.20	1977	AL001				
		3.50			51.1	2.000	1.000	CT	1.010	0.54	23.80	1977	AL001				
		4.50			51.2	3.000	1.500	CT	1.570	0.52	23.40	1977	AL001				
		4.50			51.2	3.000	1.500	CT	1.530	0.68	26.70	1977	AL001				
		4.50			51.2	3.000	1.500	CT	1.570	0.63	25.70	1977	AL001				
		2.00			51.5	1.500	0.750	CT	0.800	0.62	25.60	1977	AL001				
		---			52.3	1.997	1.001	CT	1.044	0.60	25.63	1976	MD001				

Table 7.10.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN		YIELD STRENGTH (KSI)	ALUMINUM		K(IC)	CRACK		K(IC) STAN	DATE	REFER
	FORM	THICK (IN)	THICK (IN)	ORIENT		WIDTH (IN)	THICK (IN)		DESIGN	LENGTH (IN)			
		(F)							(IN)	(KSI*SQRT IN)			
T87	P	1.50	- 300	L-T	67.0	5.000	1.468	CT	2.528	0.95	41.30	1972	85631
		1.50			67.0	5.000	1.470	CT	2.593	0.92	40.50	1972	85631
T87	P	2.00	R. T.	L-T	56.7	2.000	0.999	CT	1.012	0.50	25.40	1973	86213
		2.00			56.7	4.000	2.000	CT	2.039	0.59	27.50	1973	86688
		2.00			56.7	4.000	2.000	CT	1.998	0.58	27.40	1973	86688
		2.00			56.7	2.000	1.000	CT	1.003	0.54	26.30	1973	86213
		2.00			56.7	4.000	2.000	CT	2.044	0.60	27.70	1973	86688
T87	P	1.50			59.4	5.000	1.467	CT	2.570	0.82	33.90	1972	85631
		1.50	300	L-T	---	5.000	1.466	CT	2.581	---	25.40	1972	85631
T87		1.50			---	5.000	1.466	CT	2.573	---	34.40	1972	85631
	P	2.50	- 423	T-S	---	2.000	1.252	CT	1.100	0.58	35.00	1972	84319
T87		2.50			---	2.500	1.255	NB	1.220	1.00	47.20	1972	84319
		2.50			73.0	2.500	1.253	NB	1.240	1.10	48.80	1972	84319
		2.50			73.0	2.000	1.251	CT	1.110	0.51	33.00	1972	84319
		2.50	- 320	T-S	---	2.000	1.249	CT	1.120	0.55	31.30	1972	84319
T87		2.50			---	2.500	1.249	NB	1.220	1.00	43.30	1972	84319
		2.50			67.0	2.000	1.251	CT	1.140	0.55	31.40	1972	84319
		2.50			67.0	2.500	1.254	NB	1.230	1.00	41.60	1972	84319
		2.50	R. T.	T-S	---	2.500	1.253	NB	1.240	1.10	36.40	1972	84319
T87		2.50			---	2.000	1.252	CT	1.110	0.57	26.10	1972	84319
		2.50			59.0	2.500	1.250	NB	1.270	1.10	36.20	1972	84319
		2.50			59.0	2.000	1.252	CT	1.140	0.58	26.40	1972	84319
		1.50	- 300	T-L	67.0	5.000	1.466	CT	2.671	---	32.50	1972	85631
T87	P	1.00	R. T.	T-L	57.1	2.000	0.970	CT	1.050	0.36	21.70	1973	86213
		1.00			57.1	2.000	0.970	CT	1.059	0.38	22.20	1973	86213
T87	P	1.00	82	T-L	57.1	2.000	0.971	CT	1.034	0.40	22.70	1973	86213
T87	P	1.00	84	T-L	57.1	2.000	0.971	CT	1.051	0.37	21.90	1973	86213
		1.00			57.1	2.000	0.970	CT	1.052	0.36	21.80	1973	86213
	1.00			57.1	2.000	0.970	CT	1.072	0.36	21.70	1973	86213	

Table 7.10.2.1 (Con't)

CONDITION	ALUMINUM		2219	K(1C)	SPECIMEN		CRACK LENGTH (IN)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	---PRODUCT--- FORM THICK (IN)	TEST SPECIMEN ORIENT (F)			YIELD STRENGTH (KSI)	WIDTH (IN)						
T87-300F 100HR P	1.50	R.T.	L-T	---	5.000	1.467	CT	2.560	34.50		1972	85631
	1.50			---	5.000	1.467	CT	2.572	35.10	34.8/ 0.4	1972	85631

Table 7.10.2.2

CONDITION	ALUMINUM		2219		K(C)		CRACK LENGTH CROSS STRESS				K(C) STAN		K(C) STAN		
	FORM	THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	SPECIMEN		INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	MEAN (IN)	DEV (KSI*SQRT IN)	K(C) MEAN	STAN DEV
					W	B									
BUCKLING OF CRACK EDGES NOT RESTRAINED															
T81	S	0.06	R.T.	L-T	53.0	0.062	0.627	1.034	34.70	26.60	38.65*	56.24*	1973	86213	
		0.06			53.0	0.062	0.627	0.875	34.60	36.30	38.34*	48.36*	1973	86213	
T81	S	0.06	R.T.	T-L	53.0	0.062	0.626	0.863	34.50	35.60	37.81*	47.19*	1973	86213	
		0.06			53.0	0.062	0.628	0.899	34.20	35.50	37.57*	48.32*	1973	86213	
BUCKLING OF CRACK EDGES NOT RESTRAINED															
T851	S	0.12	R.T.	L-T	50.6	0.123	1.090	1.700	---	33.00	47.07*	67.98*	1973	86213	
		0.12			50.6	0.127	1.070	1.860	---	32.50	45.78*	74.10*	1973	86213	
		0.12			50.6	0.127	1.090	1.720	---	32.10	45.79*	66.95*	1973	86213	
		0.12			51.1	0.127	1.090	1.820	---	32.10	45.79*	71.31*	1973	86213	
		0.12			51.1	0.127	1.110	1.760	---	31.60	45.64*	67.57*	1973	86213	
		0.12			51.1	0.126	1.100	1.930	---	31.90	45.79*	76.19*	1973	86213	
		0.12			52.0	0.127	1.080	1.670	---	31.70	45.50*	64.11*	1973	86213	
		0.12			52.0	0.127	1.080	1.740	---	32.10	45.50*	67.79*	1973	86213	
		0.12			52.0	0.127	1.100	2.000	---	31.40	45.07*	78.71*	1973	86213	
		0.12			52.0	0.127	1.130	---	---	31.00	45.33*	---	1973	86213	
		0.12			52.0	0.126	1.080	1.740	---	31.50	44.65*	66.52*	1973	86213	
T851	P	1.00	R.T.	L-T	50.6	1.000	7.000	10.500	---	18.30	65.72	90.21	1973	86213	
		1.00			50.6	1.000	7.000	10.350	---	19.60	70.39	95.32*	1973	86213	
		1.00			50.6	1.000	7.000	9.770	---	19.30	69.31	89.12	1973	86213	
		1.00			50.6	1.000	7.000	10.200	---	19.60	70.39	94.09	1973	86213	
		1.00			51.1	1.000	7.000	10.050	---	16.00	57.46	75.75	1973	86213	
		1.00			51.1	1.000	7.000	10.100	---	16.30	58.53	77.91	1973	86213	
		1.00			51.1	1.000	7.000	9.450	---	16.00	57.46	71.81	1973	86213	
		1.00			52.0	1.000	7.000	9.750	---	15.80	56.74	72.83	1973	86213	
		1.00			52.0	1.000	7.000	10.400	---	18.60	66.79	90.86	1973	86213	
		1.00			52.0	1.000	7.000	10.500	---	18.80	67.51	92.67	1973	86213	
		1.00			52.0	1.000	7.000	10.870	---	18.00	64.64	71.79	1973	86213	
		1.00			52.0	1.000	7.000	12.000	---	18.30	65.72	64.2/ 5.3 103.63* 84.7/ 9.0	1973	86213	

*NOTE- NET SECTION STRESS EXCEEDS 90% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

Table 7.10.2.2 (Con't)

CONDITION	ALUMINUM		2219		K(C)		CRACK LENGTH CROSS STRESS						K(APP) STAN		K(C) STAN		
	--PRODUCT-- FORM THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	---SPECIMEN---		INIT FINAL		ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	STAN DEV	K(C) (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
				WIDTH (IN)	THICK (IN)	2A(D) 2A(F)	2A(E) 2A(F)										
T851	S	0.12	R.T.	T-L	49.3	3.000	0.126	1.100	1.680	---	30.10	43.20*	61.24*	---	---	---	1973 86213
		0.12			49.3	3.000	0.127	1.090	1.560	---	27.20	41.65*	55.25*	---	---	---	1973 86213
		0.12			49.3	3.000	0.126	1.100	1.740	---	29.80	42.77*	62.93*	---	---	---	1973 86213
		0.12			49.3	3.000	0.127	1.100	1.560	---	29.50	42.34*	55.81*	---	---	---	1973 86213
		0.12			50.8	3.000	0.127	1.080	1.600	---	28.80	40.82*	55.82*	---	---	---	1973 86213
		0.12			50.8	3.000	0.127	1.100	1.620	---	30.00	43.06*	58.85*	---	---	---	1973 86213
		0.12			50.8	3.000	0.127	1.090	1.590	---	28.30	40.37*	54.52*	---	---	---	1973 86213
		0.12			50.8	3.000	0.127	1.080	1.560	---	30.40	43.09*	57.52*	---	---	---	1973 86213
		0.12			51.2	3.000	0.127	1.100	1.580	---	30.30	43.49*	58.02*	---	---	---	1973 86213
		0.12			51.2	3.000	0.127	1.080	1.590	---	30.30	42.95*	58.37*	---	---	---	1973 86213
		0.12			51.2	3.000	0.127	1.100	1.480	---	29.20	41.91*	52.67*	---	---	---	1973 86213
		0.12			51.2	3.000	0.127	1.120	1.600	---	29.20	42.44*	56.59*	---	---	---	1973 86213
T851	P	1.00	R.T.	T-L	49.3	20.000	1.000	7.000	9.500	---	14.90	53.51	67.17	---	---	---	1973 86213
		1.00			49.3	20.000	1.000	7.000	10.100	---	15.10	54.23	71.81	---	---	---	1973 86213
		1.00			49.3	20.000	1.000	7.000	10.000	---	14.70	52.79	69.28	---	---	---	1973 86213
		1.00			49.3	20.000	1.000	7.000	9.300	---	14.80	53.15	65.54	---	---	---	1973 86213
		1.00			50.2	20.000	1.000	7.000	10.050	---	13.00	46.68	61.55	---	---	---	1973 86213
		1.00			50.2	20.000	1.000	7.000	9.200	---	13.50	48.48	59.25	---	---	---	1973 86213
		1.00			50.2	20.000	1.000	7.000	9.990	---	13.40	48.12	63.10	---	---	---	1973 86213
		1.00			50.2	20.000	1.000	7.000	9.850	---	13.40	48.12	62.32	---	---	---	1973 86213
		1.00			51.2	20.000	1.000	7.000	9.650	---	14.10	50.63	64.42	---	---	---	1973 86213
		1.00			51.2	20.000	1.000	7.000	10.000	---	14.80	53.15	69.76	---	---	---	1973 86213
		1.00			51.2	20.000	1.000	7.000	10.000	---	15.00	53.87	70.70	---	---	---	1973 86213
		1.00			51.2	20.000	1.000	7.000	10.000	---	15.10	54.23	71.17	---	---	---	1973 86213

BUCKLING OF CRACK EDGES RESTRAINED

CONDITION	S	0.06	-423	L-T	70.7	5.500	0.068	0.300	BUCKLING OF CRACK EDGES RESTRAINED		K(C) STAN	DATE	REFER
									MEAN	STD. DEV.			
		0.06			70.7	5.500	0.068	0.400	---	66.70	45.87*	---	1971 80104
		0.06			70.7	5.500	0.068	0.610	---	64.60	51.37*	---	1971 80104
		0.06			70.7	5.500	0.067	0.610	---	61.50	60.66*	---	1971 80104
		0.06			70.7	5.500	0.067	0.490	---	62.60	55.19*	---	1971 80104

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

Table 7.10.2.2 (Con't)

ALUMINUM		2219		K(C)		CRACK LENGTH CROSS STRESS																																
CONDITION	--PRODUCT-- FORM	TEST SPEC THICK (IN)	TEMP OR (F)	YIELD STR (KSI)	--SPECIMEN--		INIT		FINAL		ONSET		MAX		K(AFP) STAN		K(C) STAN																					
					WIDTH (IN)	THICK (IN)	(IN)	(IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI)	(KSI)	MEAN (KSI)	DEV (IN)	MEAN (KSI)	DEV (IN)	DATE	REFER																		
					W	B	2A(D)	2A(F)	9(O)	9(MAX)																												
T87	S	0.06	- 423	L-T	70.7	6.700	0.068	0.820	---	58.20	66.67*	---	---	---	---	---	---	---	1971	80104																		
																					0.06	6.700	0.069	1.030	---	59.70	71.90*	---	---	---	---	---	---	---	---	---	---	---
																					0.06	6.700	0.068	1.180	---	53.60	74.40*	---	---	---	---	---	---	---	---	---	---	---
T87	S	0.06	- 423	L-T	70.7	6.700	0.068	0.890	---	57.50	68.74*	---	---	---	---	---	---	---	1971	80104																		
																					0.06	6.700	0.062	5.060	6.410	---	26.30	79.13	---	92.91	---	---	---	---	---	---	---	---
																					0.06	6.700	0.061	5.000	5.980	---	26.30	78.49	78.8/	0.5	88.35	90.6/	3.2	1966	69759			
T87	S	0.06	- 320	L-T	64.5	5.500	0.068	0.620	---	57.10	56.80*	---	---	---	---	---	---	---	1971	80104																		
																					0.06	5.500	0.069	0.420	---	61.50	50.13*	---	---	---	---	---	---	---	---	---	---	
																					0.06	5.500	0.068	0.480	---	60.20	52.52*	---	---	---	---	---	---	---	---	---	---	---
T87	S	0.06	- 320	L-T	64.5	5.500	0.068	0.330	---	63.20	45.60*	---	---	---	---	---	---	---	1971	80104																		
																					0.06	6.700	0.069	1.200	---	51.10	71.58*	---	---	---	---	---	---	---	---	---	---	---
																					0.06	6.700	0.067	0.880	---	55.90	66.43*	---	---	---	---	---	---	---	---	---	---	---
T87	S	0.06	R. T.	L-T	55.0	5.500	0.068	0.620	---	47.90	47.64*	---	---	---	---	---	---	---	1971	80104																		
																					0.06	5.500	0.067	0.400	---	51.30	40.80*	---	---	---	---	---	---	---	---	---	---	---
																					0.06	5.500	0.067	0.520	---	49.80	45.26*	---	---	---	---	---	---	---	---	---	---	---
T87	S	0.06	R. T.	L-T	55.0	5.500	0.068	0.330	---	52.50	37.88*	---	---	---	---	---	---	---	1971	80104																		
																					0.06	6.700	0.067	0.910	---	47.30	57.20*	---	---	---	---	---	---	---	---	---	---	---
																					0.06	6.700	0.068	1.000	---	46.10	58.58*	---	---	---	---	---	---	---	---	---	---	---
T87	S	0.10	R. T.	L-T	58.5	3.500	0.100	0.750	0.980	---	46.40	51.84*	---	---	---	---	---	---	1962	62306																		
																					0.10	6.000	0.100	2.000	2.460	---	34.60	65.90*	---	---	---	---	---	---	---	---	---	---
																					0.10	12.000	0.100	2.000	2.680	---	41.30	74.48*	---	---	---	---	---	---	---	---	---	---
T87	S	0.10	R. T.	L-T	58.5	12.000	0.100	4.000	4.770	---	27.90	75.15	---	---	---	---	---	---	1962	62306																		
																					0.10	24.000	0.100	20.000	20.650	---	6.40	70.51	---	---	---	---	---	---	---	---	---	---
																					0.10	24.000	0.100	4.000	5.730	---	33.90	86.46	---	---	---	---	---	---	---	---	---	---

*NOTE-- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

Table 7.10.2.2 (Con't)

CONDITION	ALUMINUM		CRACK LENGTH CROSS STRESS										K(C)				
	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPEC OR	YIELD STR (KSI)	---SPECIMEN---					CRACK LENGTH CROSS STRESS					K(C) (KSI*SQRT IN)	STAN DEV
						WIDTH (IN)	THICK (IN)	B	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	MEAN DEV			
T87	S	0.10	R. T.	L-T	58.5	24.000	0.100	8.000	9.580	---	24.00	91.42	103.46	1962	62306		
		0.10			58.5	24.000	0.100	18.000	19.430	---	7.40	63.61	75.31	1962	62306		
		0.10			58.5	24.000	0.100	18.000	18.620	---	8.40	72.20	77.36	1962	62306		
		0.10			58.5	24.000	0.100	12.000	13.650	---	17.80	91.90	104.11	1962	62306		
		0.10			58.5	24.000	0.100	2.000	2.590	---	42.40	75.48	86.14*	1962	62306		
		0.10			58.5	24.000	0.100	1.000	1.400	---	48.40	60.73*	71.93*	1962	62306		
		0.10			58.5	24.000	0.100	0.500	0.770	---	54.40	48.22*	78.8/11.1	59.87*	90.6/19.0		
T87	S	0.10	R. T.	L-T	58.5	30.000	0.100	18.000	19.700	---	12.50	86.70	97.03	1962	62306		
T87	S	0.10	R. T.	L-T	58.5	36.000	0.100	4.000	5.450	---	34.00	85.88	100.91	1962	62306		
T87	S	0.10	R. T.	L-T	58.5	48.000	0.100	4.000	5.580	---	34.90	87.86	104.19	1962	62306		
		0.10			58.5	48.000	0.100	12.000	13.030	---	23.20	104.79	120.17	1962	62306		
		0.10			58.5	48.000	0.100	36.000	37.170	---	7.90	96.03	102.47	1962	62306		
		0.10			58.5	48.000	0.100	41.900	43.180	---	4.30	78.34	89.35	1962	62306		
		0.10			58.5	48.000	0.100	24.000	25.720	---	15.40	112.45	119.93	1962	62306		
		0.10			58.5	48.000	0.100	8.000	9.250	---	28.20	101.71	110.02	1962	62306		
		0.10			58.5	48.000	0.100	12.000	14.200	---	24.50	110.66	98.8/12.4	122.38	109.8/12.1		

BUCKLING OF CRACK EDGES RESTRAINED

BUCKLING OF CRACK EDGES NOT RESTRAINED

T87	S	0.03	- 423	L-T	74.0	12.000	0.032	1.210	2.020	---	48.10	66.73	87.21	1966	66103
T87	S	0.03	- 423	L-T	74.0	16.000	0.032	4.240	7.030	---	27.80	75.02	105.20	1966	66103
T87	S	0.12	- 423	L-T	74.0	12.000	0.125	1.230	1.940	---	46.20	64.64	81.97	1966	66103
T87	S	0.12	- 423	L-T	74.0	16.000	0.125	4.830	6.310	---	26.90	78.55	93.86	1966	66103
T87	S	0.06	R. T.	L-T	59.2	2.000	0.065	0.625	1.110	---	38.10	40.16*	62.72*	1973	86213
		0.06			59.2	2.000	0.064	0.622	0.810	---	38.10	40.08*	47.92*	1973	86213

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

Table 7.10.2.2 (Con't)

CONDITION	--PRODUCT--		TEST SPEC OR TEMP (F)	YIELD STR (KSI)	SPECIMEN				CRACK LENGTH CROSS STRESS				ALUMINUM		K(C)	K(C) STAN DEV	K(C) MEAN	K(C) STAN DEV	DATE	REFER	
	FORM	THICK (IN)			WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI)	K(APP) STAN DEV (KSI)	K(C) STAN DEV (KSI)	K(C) MEAN (KSI)							K(C) STAN DEV (KSI)
T87	S	0.06	R.T.	L-T	59.2	2.000	0.064	0.623	0.880	---	37.80	39.76*	50.63*	1973	86213						
		0.06			59.2	2.000	0.064	0.609	0.940	---	38.70	40.13*	54.68*	1973	86213						
		0.06			59.2	2.000	0.064	0.625	1.080	---	37.80	39.84*	60.54*	1973	86213						
T87	S	0.06	R.T.	L-T	57.7	15.930	0.061	5.000	6.280	---	22.80	68.08	79.36	1966	69759						
T87	S	0.06	R.T.	L-T	57.7	16.290	0.062	5.000	6.360	---	21.50	64.01	75.15	1966	69759						
		0.06			57.7	16.290	0.062	4.980	5.910	---	23.10	68.60	76.70	1966	69759						
T87	S	0.12	R.T.	L-T	58.1	2.990	0.125	0.993	1.250	---	36.40	48.79*	57.31*	1973	86213						
		0.12			58.1	2.990	0.126	0.995	1.300	---	35.90	48.18*	58.25*	1973	86213						
		0.12			58.1	2.990	0.126	0.992	1.250	---	36.30	48.66*	57.15*	1973	86213						
		0.12			54.7	3.000	0.125	1.090	1.820	---	32.50	46.36*	72.20*	1973	86213						
		0.12			54.7	3.000	0.125	1.080	1.800	---	32.50	46.07*	71.28*	1973	86213						
T87	P	0.25	R.T.	L-T	57.6	3.000	0.247	1.000	1.680	---	34.30	46.19*	69.79*	1973	86213						
		0.25			57.6	3.000	0.247	1.160	1.790	---	31.40	46.77*	68.43*	1973	86213						
		0.25			57.6	3.000	0.247	1.257	2.060	---	29.70	46.89*	77.72*	1973	86213						
T87	P	0.25	R.T.	L-T	56.0	4.000	0.247	1.130	1.900	---	32.10	46.94*	75.14*	1973	86213						
		0.25			56.0	4.000	0.244	1.330	2.290	---	32.40	50.30*	76.47*	1973	86213						
		0.25			56.0	4.000	0.245	1.430	2.970	---	31.00	50.50*	85.35*	1973	86213						
		0.25			56.0	4.000	0.246	1.330	2.260	---	32.20	49.99*	76.35*	1973	86213						
		0.25			57.6	4.000	0.246	1.330	2.030	---	34.40	53.41*	73.49*	1973	86213						
		0.25			57.6	4.000	0.246	1.330	2.250	---	34.10	52.94*	80.49*	1973	86213						
		0.25			57.6	4.000	0.247	1.410	2.310	---	33.20	53.57*	80.58*	1973	86213						
		0.25			56.0	4.000	0.256	1.330	2.160	---	32.10	49.84*	72.71*	1973	86213						
		0.25			56.0	4.000	0.255	1.440	2.470	---	30.90	50.58*	80.95*	1973	86213						
		0.25			56.0	4.000	0.255	1.330	2.180	---	32.40	50.30*	74.06*	1973	86213						
T87	S	0.06	R.T.	T-L	59.0	2.000	0.064	0.623	0.900	---	36.10	37.97*	49.22*	1973	86213						
		0.06			59.0	2.000	0.064	0.625	0.960	---	36.70	38.68*	52.78*	1973	86213						
		0.06			59.0	2.000	0.064	0.619	0.880	---	37.40	39.18*	50.09*	1973	86213						
	0.06			59.0	2.000	0.064	0.622	0.870	---	36.50	38.39*	48.49*	1973	86213							

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

Table 7.10.2.2 (Con't)

CONDITION	ALUMINUM		2219		K(C)		CRACK LENGTH GROSS STRESS										K(C) STAN						
	---PRODUCT--- FORM	THICK (IN)	TEST SPEC OR	YIELD STR (KSI)	---SPECIMEN---		W		B		INIT		FINAL		ONSET		MAX		K(APP) MEAN DEV		K(C) STAN		
					WIDTH (IN)	THICK (IN)	W	B	2A(O)	2A(F)	B(O)	B(MAX)	INIT (IN)	FINAL (IN)	ONSET (KBI)	MAX (KBI)	K(APP) (KBI*SQRT IN)	MEAN (KBI*SQRT IN)	DEV	STAN	MEAN (KBI*SQRT IN)	DEV	DATE
T87	S	0.06	R.T.	59.0	2.000	0.064	0.625	0.980	---	36.50	38.47*	---	---	---	---	---	---	---	53.44*	---	---	1973	86213
T87	S	0.12	R.T.	58.6	2.990	0.126	0.990	1.300	---	33.90	45.38*	---	---	---	---	---	---	---	55.00*	---	---	1973	86213
		0.12		58.6	2.990	0.126	0.994	1.280	---	34.10	45.77*	---	---	---	---	---	---	---	54.67*	---	---	1973	86213
		0.12		58.6	2.990	0.126	0.991	1.280	---	33.90	45.38*	---	---	---	---	---	---	---	54.35*	---	---	1973	86213
		0.12		58.6	2.990	0.124	0.992	1.350	---	34.30	45.98*	---	---	---	---	---	---	---	57.34*	---	---	1973	86213
		0.12		55.9	3.000	0.124	1.070	1.760	---	30.60	43.10*	---	---	---	---	---	---	---	65.43*	---	---	1973	86213
		0.12		55.9	3.000	0.124	1.080	1.690	---	30.50	43.23*	---	---	---	---	---	---	---	62.44*	---	---	1973	86213
T87	P	0.25	R.T.	57.2	3.000	0.247	1.000	1.530	---	32.00	43.10*	---	---	---	---	---	---	---	59.47*	---	---	1973	86213
		0.25		57.2	3.000	0.247	1.160	1.740	---	29.20	43.50*	---	---	---	---	---	---	---	61.66*	---	---	1973	86213
		0.25		57.2	3.000	0.247	1.120	1.710	---	30.40	44.18*	---	---	---	---	---	---	---	63.01*	---	---	1973	86213
T87	P	0.25	R.T.	59.9	4.000	0.246	1.330	2.120	---	28.60	44.40	---	---	---	---	---	---	---	63.62*	---	---	1973	86213
		0.25		59.9	4.000	0.246	1.330	2.060	---	28.70	44.56	---	---	---	---	---	---	---	62.14*	---	---	1973	86213
		0.25		59.9	4.000	0.249	1.460	2.310	---	26.60	43.95	---	---	---	---	---	---	---	64.56*	---	---	1973	86213
		0.25		57.2	4.000	0.246	1.330	2.040	---	30.80	47.82*	---	---	---	---	---	---	---	66.09*	---	---	1973	86213
		0.25		57.2	4.000	0.246	1.440	2.170	---	29.00	47.47	---	---	---	---	---	---	---	65.99*	---	---	1973	86213
		0.25		55.6	4.000	0.255	1.440	2.240	---	27.80	45.50	---	---	---	---	---	---	---	65.32*	---	---	1973	86213
		0.25		55.6	4.000	0.255	1.330	2.060	---	28.90	44.87	---	---	---	---	---	---	---	62.57*	---	---	1973	86213
		0.25		55.6	4.000	0.256	1.330	2.070	---	29.00	45.02	---	---	---	---	---	---	---	63.07*	---	---	1973	86213

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.10.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219
CONDITION: T851
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.30	R=+0.50		
DELTA K	A: 4.29	.417			
MIN	B: 6.14		2.02		
	C:				
	D:				
	5.00	.741			
	6.00	1.38			
	7.00	2.23	2.81		
	8.00	3.34	4.10		
	9.00	4.76	6.05		
	10.00	6.55	9.15		
	13.00	15.2	36.8		
	16.00	32.5			
DELTA K	A: 19.30	71.4			
MAX	B: 15.80		161.		
	C:				
	D:				
ROOT MEAN SQUARE		9.32	21.19		
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM:
 SPECIMEN TYPE: CT
 ORIENTATION:
 FREQUENCY: 30.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.000"
 REFERENCES:UD010

ALUM.
 ALLOY

2219

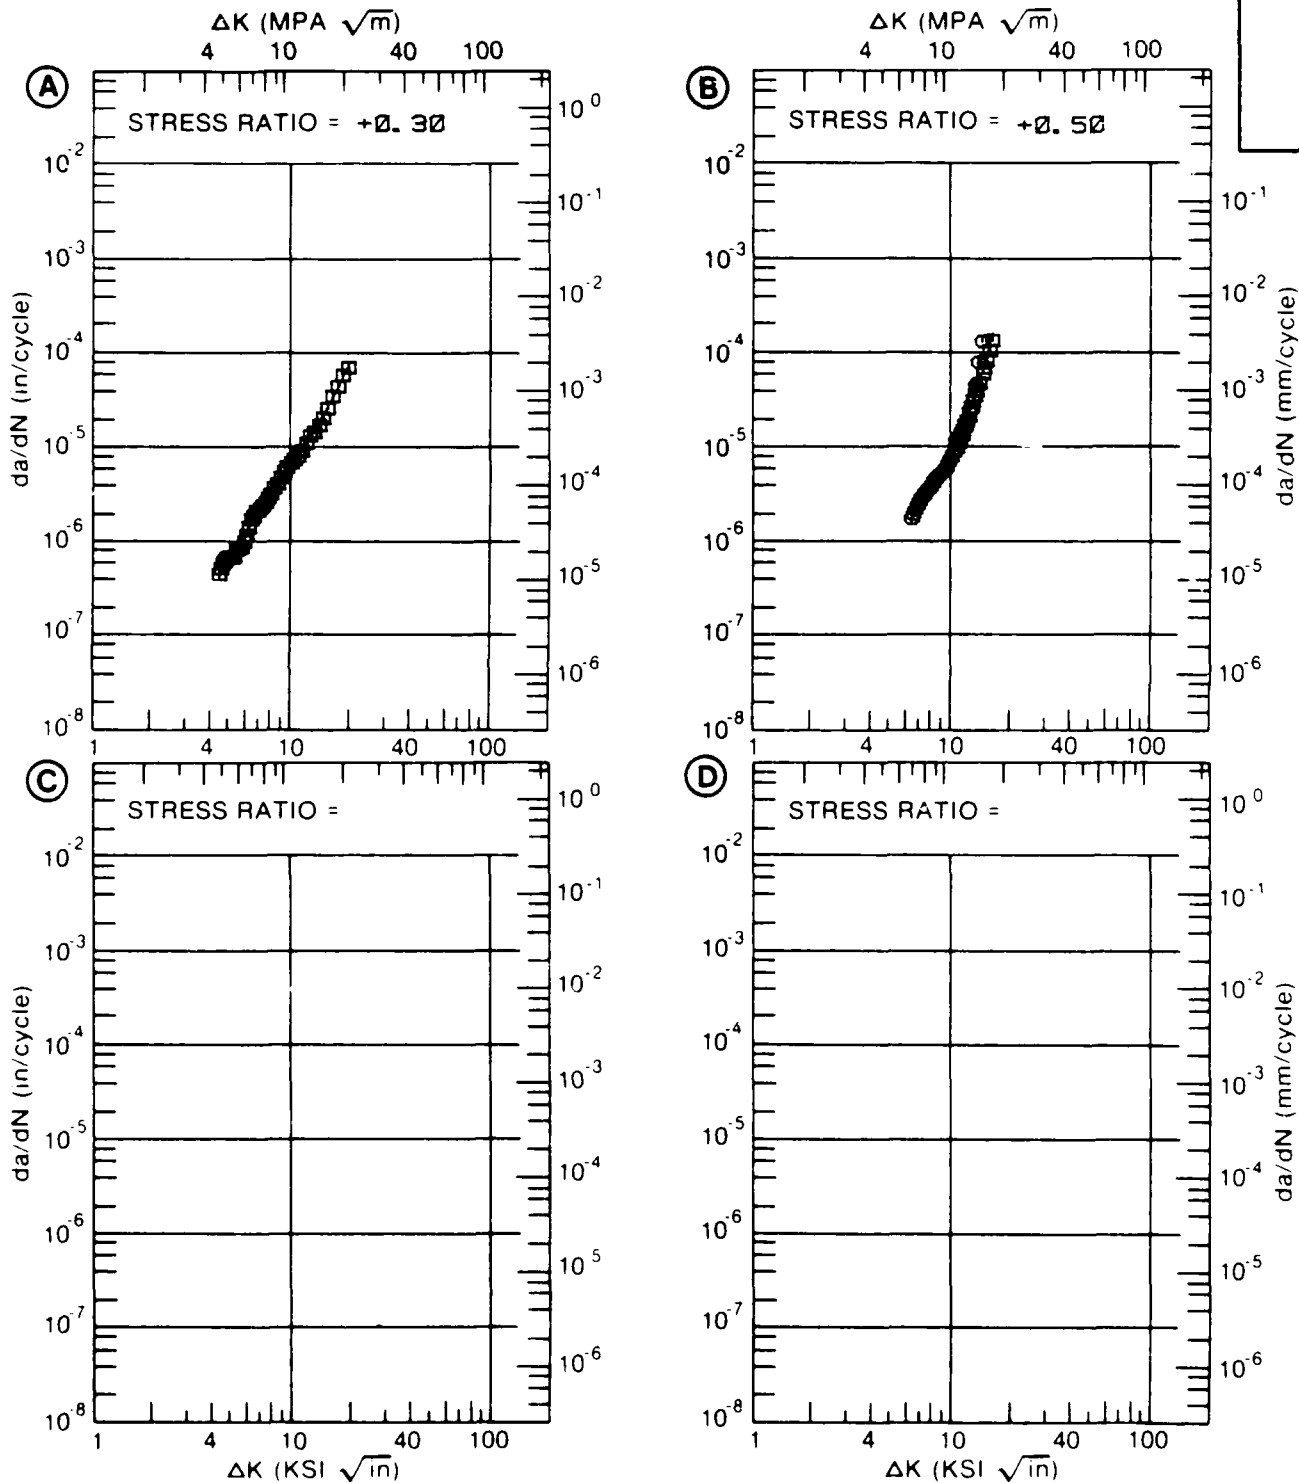


Figure 7.10.3.1

TABLE 7.10.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219
CONDITION: T851
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	R=-1.00			
DELTA K MIN	A: 5.84	.966		
	6.00	1.06		
	7.00	1.71		
	8.00	2.44		
	9.00	3.23		
	10.00	4.09		
	13.00	7.45		
	16.00	13.1		
	20.00	28.5		
DELTA K MAX	A: 20.70	32.9		

ROOT MEAN SQUARE 7.13
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM:
 SPECIMEN TYPE: CCP
 ORIENTATION:
 FREQUENCY: 5.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: UD010

ALUM.
ALLOY

2219

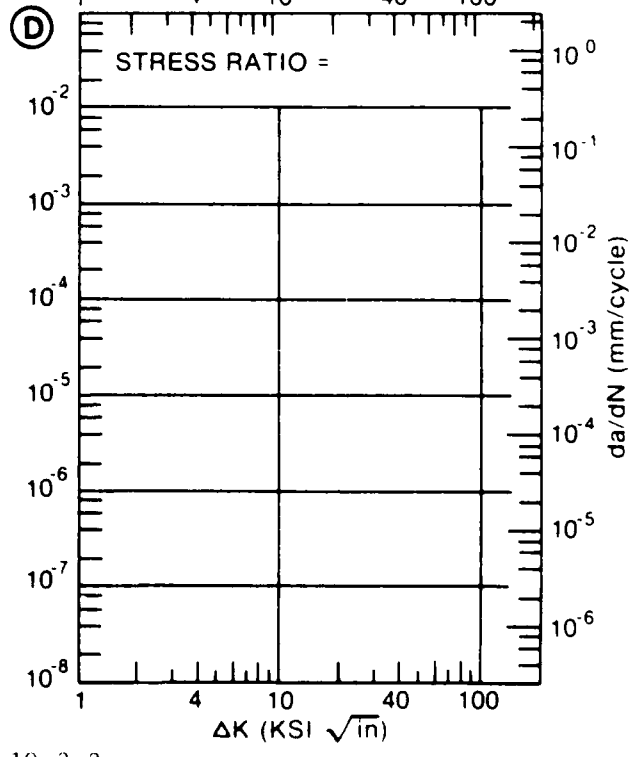
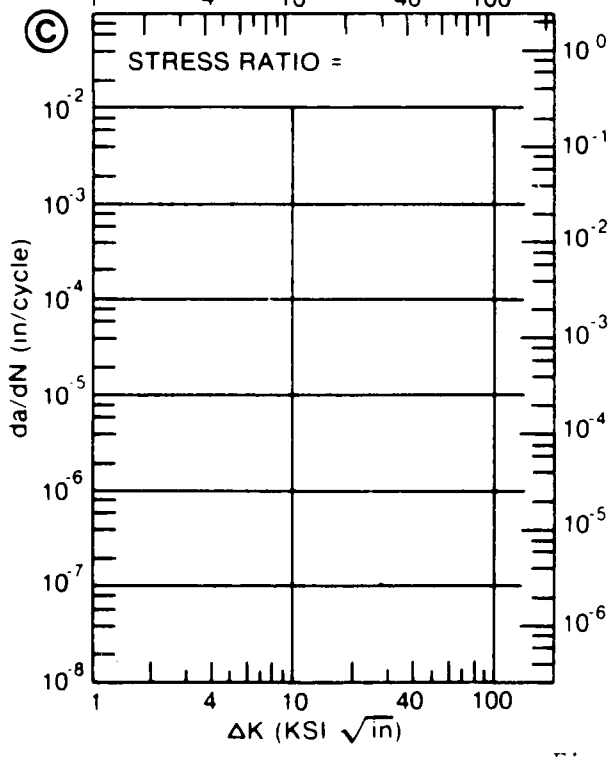
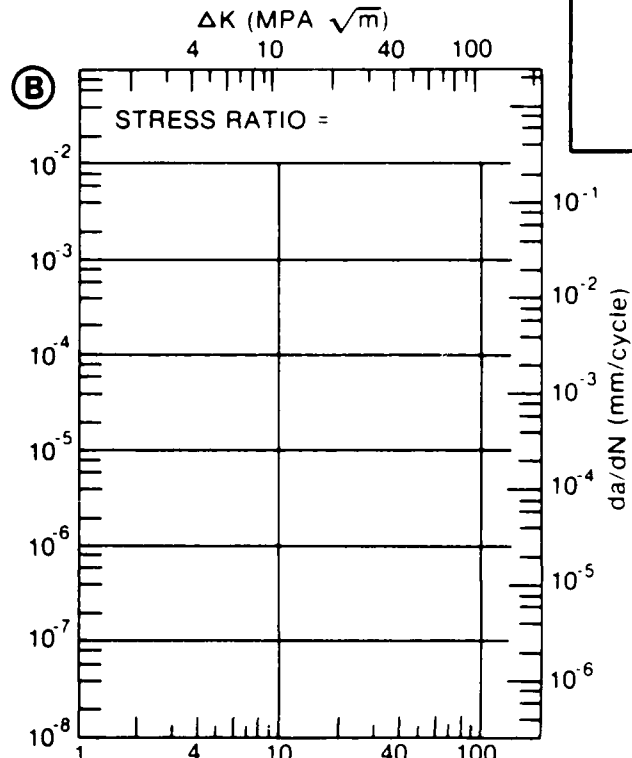
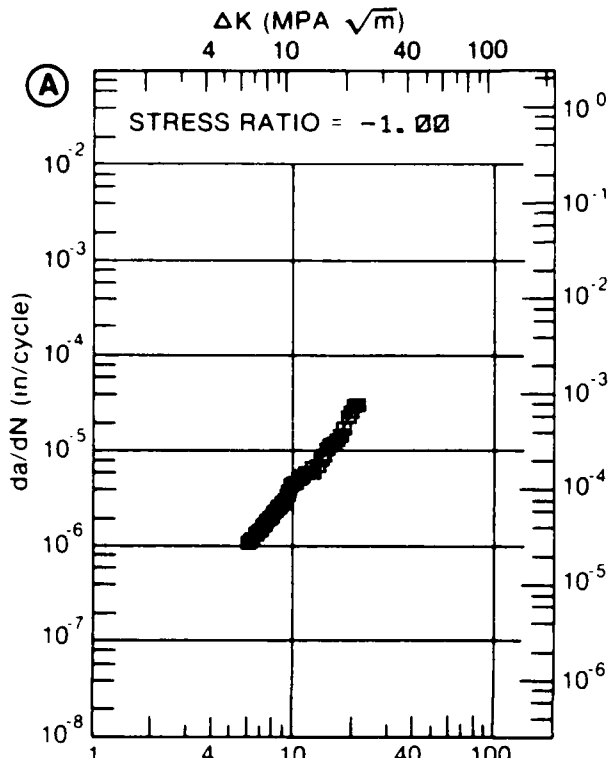


Figure 7.10.3.2

TABLE 7.10.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		LAB AIR			
DELTA K	A: 2.93	.02			
MIN	B: 1				
	C:				
	D:				
	3.00	.0239			
	3.50	.0669			
	4.00	.149			
	5.00	.477			
	6.00	1.09			
	7.00	2.03			
	8.00	3.35			
	9.00	5.10			
	10.00	7.33			
	13.00	17.8			
	16.00	36.9			
DELTA K	A: 19.20	73.3			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		13.25			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	3			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM:
 SPECIMEN TYPE: CT
 ORIENTATION:
 STRESS RATIO: +0.10
 FREQUENCY: 5.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.000"
 REFERENCES:UD010

ALUM.
 ALLOY

2219

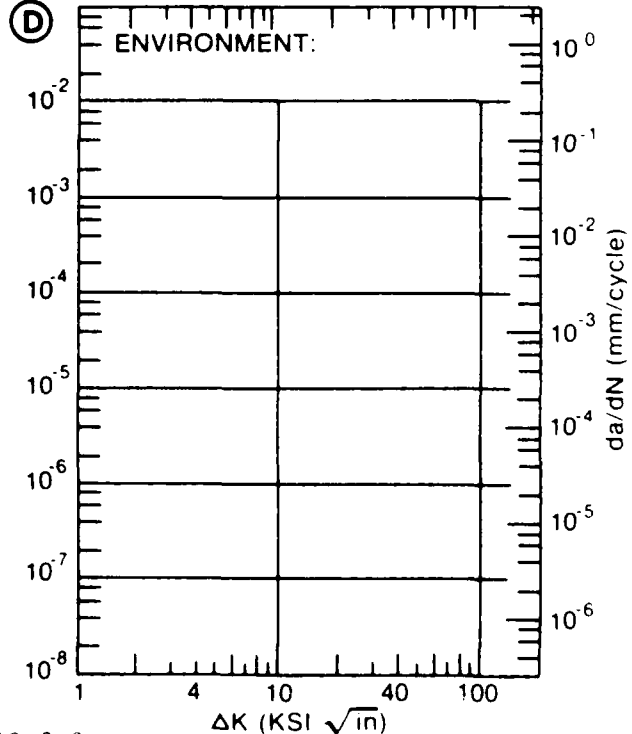
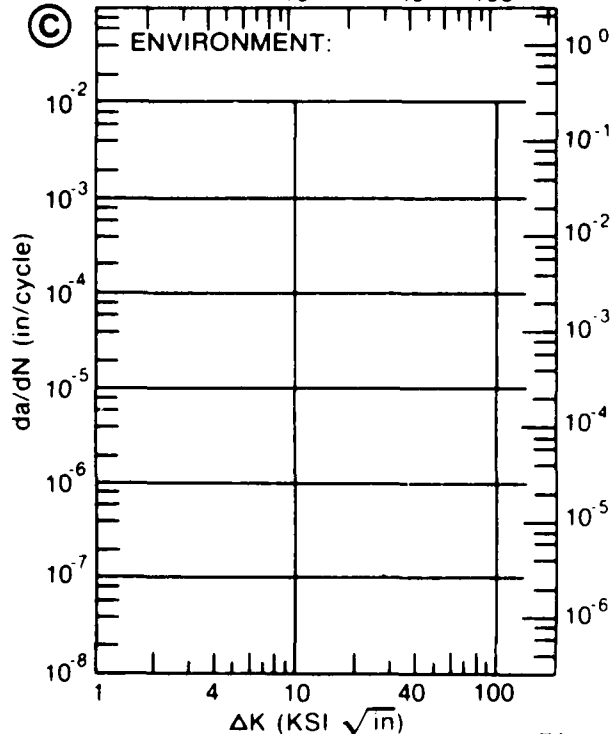
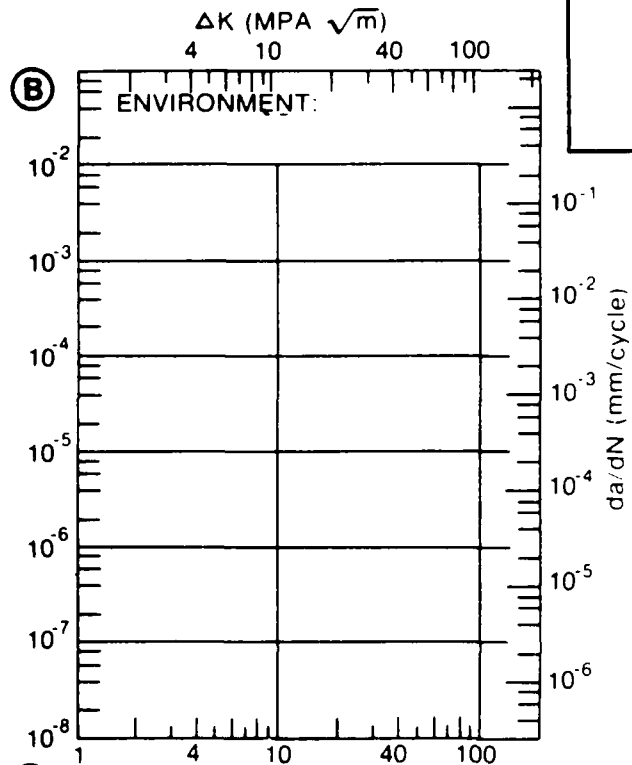
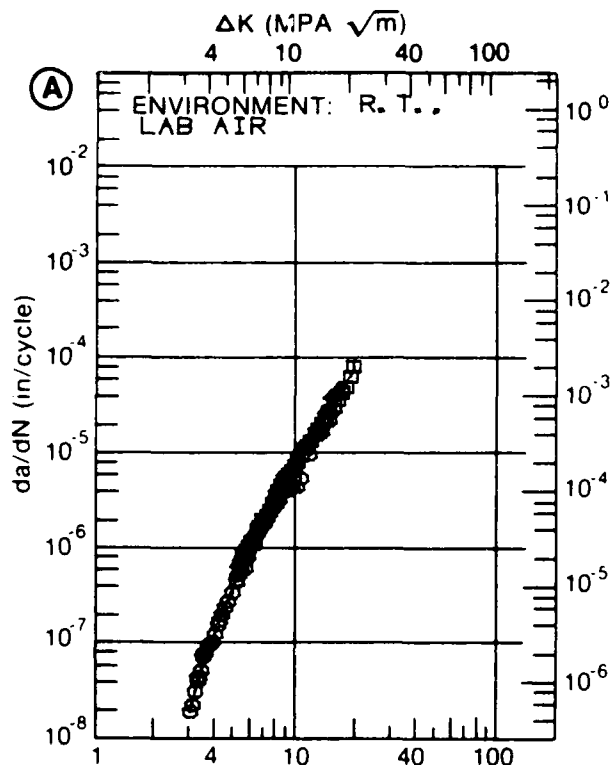


Figure 7.10.3.3

TABLE 7.10.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.4 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 0.10		F(HZ)= 5.00	
DELTA K	A: 5.00	2.04			
MIN	B: 2.45		.111		
	C:				
	D:				
	2.50		.122		
	3.00		.245		
	3.50		.429		
	4.00		.762		
	5.00		3.08		
	6.00	7.93			
	7.00	50.4			
DELTA K	A: 7.01	51.9			
MAX	B: 5.01		3.13		
	C:				
	D:				
ROOT MEAN SQUARE		22.21	11.84		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM:
 SPECIMEN TYPE: CT
 ORIENTATION:
 STRESS RATIO: +0.80
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.000"
 REFERENCES:UD010

ALUM. ALLOY
2219




Figure 7.10.3.4

TABLE 7.10.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.5 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-1.00	R=-0.30	R=-0.10	R=+0.00
DELTA K	A: 6.61 :	2.98			
MIN	B: 6.34 :		1.80		
	C: 6.17 :			1.23	
	D: 6.25 :				.791
	7.00 :	2.86	2.37	2.07	1.25
	8.00 :	3.30	3.50	3.36	2.05
	9.00 :	4.61	4.99	4.94	3.08
	10.00 :	6.81	6.88	6.79	4.33
	13.00 :	17.7	15.2	13.9	9.59
	16.00 :		27.6	24.0	17.6
	20.00 :		52.5	44.9	34.6
	25.00 :		107.	93.6	
	30.00 :		214.	193.	
	35.00 :		428.	401.	
	40.00 :		865.	837.	
	50.00 :		3618.	3707.	
	60.00 :			16519.	
DELTA K	A: 14.09 :	21.3			
MAX	B: 59.68 :		14767.		
	C: 63.72 :			28766.	
	D: 23.46 :				58.2
ROOT MEAN SQUARE		18.45	38.38	20.98	4.31
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	2	3	1
SUMMARY	1.25-2.0				
(NP/NA)	>2.0		1		

CONDITION/HT: T851
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R.T., LAB AIR

YIELD STRENGTH: 46.0 KSI
 ULT. STRENGTH: 62.0 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: RI003

ALUM. ALLOY
2219

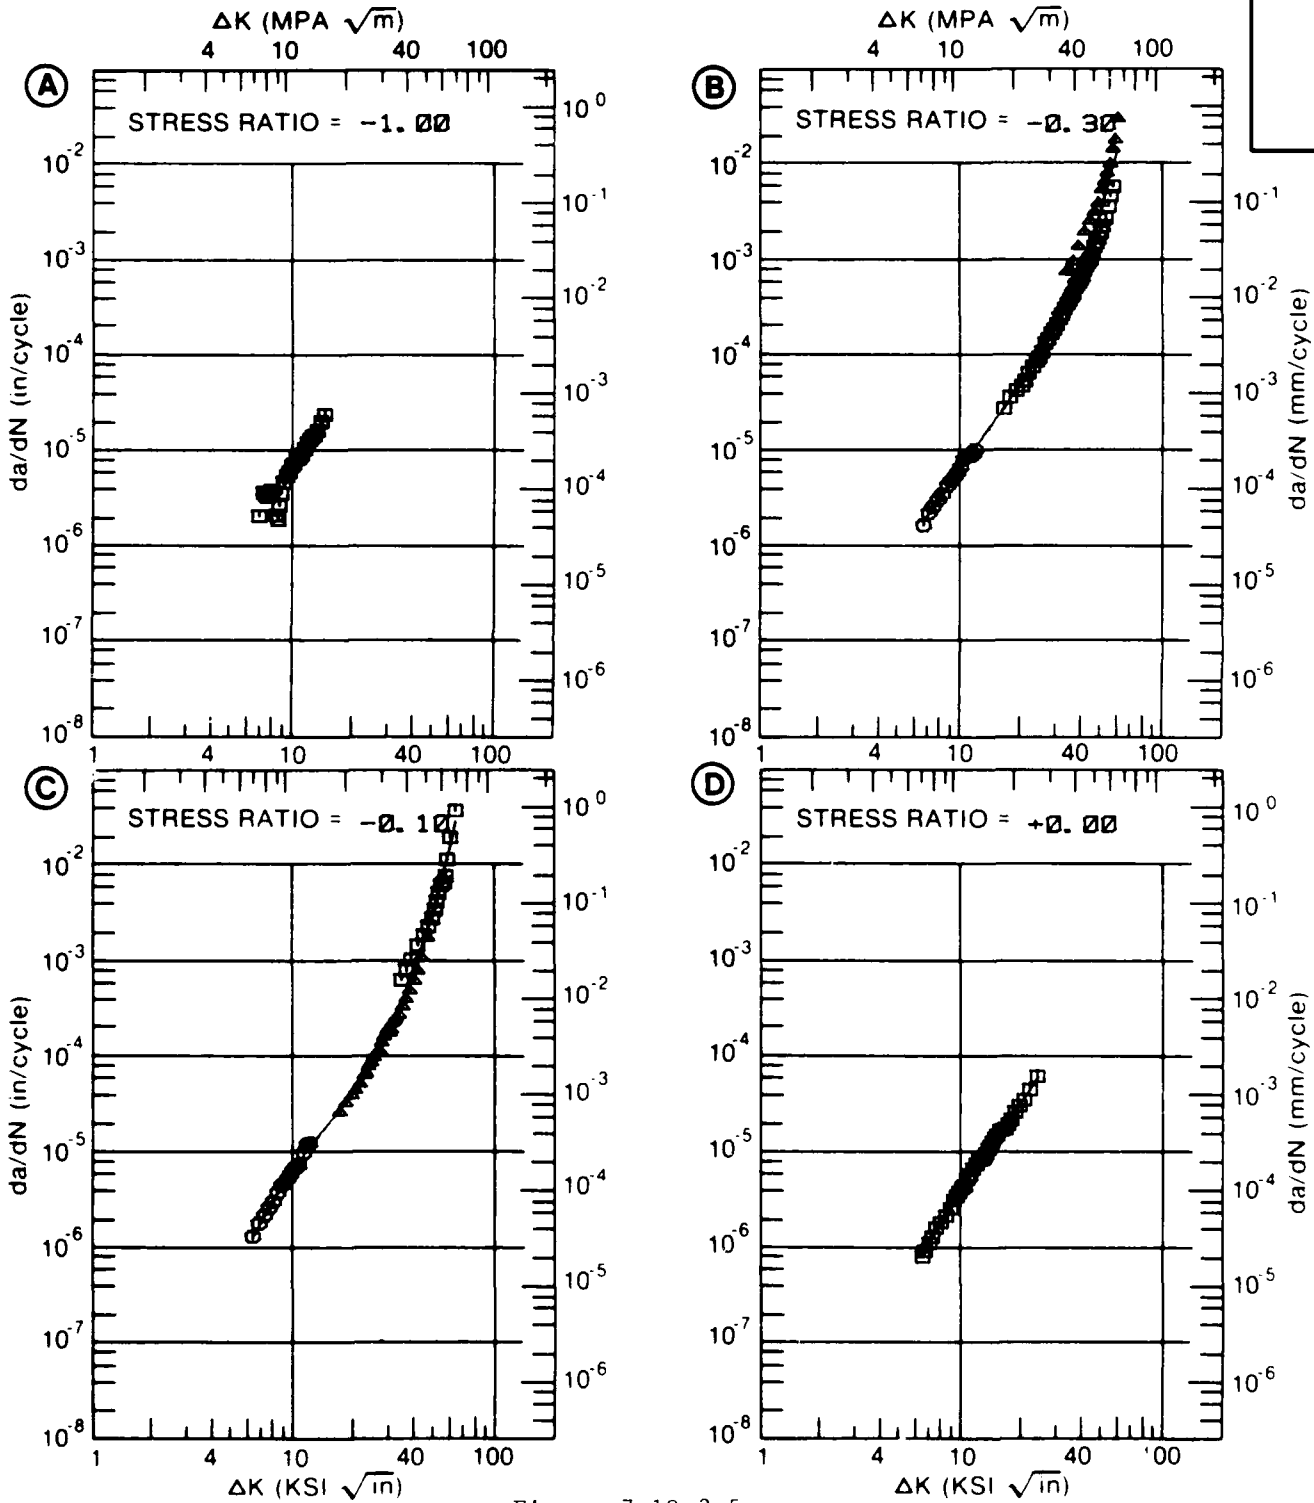


Figure 7.10.3.5

TABLE 7.10.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.6 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219					
CONDITION: T851					
ENVIRONMENT: R. T. / LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.01	R=+0.20	R=+0.30	R=+0.70
A:	15.91	24.3			
DELTA K B:	14.07		25.9		
MIN C:	3.99			332	
D:	4.65				977
	4.00			334	
	5.00			698	1.39
	6.00			1.33	2.59
	7.00			2.32	3.94
	8.00			3.73	6.02
	9.00			5.56	10.1
	10.00			7.86	17.8
	13.00			18.2	60.1
	16.00	24.7	42.1	35.5	144.
	20.00	46.2	90.9	76.3	1174.
	25.00	95.0	196.	179.	
	30.00	185.	392.	392.	
	35.00	344.	771.	824.	
	40.00	614.	1523.		
	50.00	1788.			
DELTA K A:	50.85	1949.			
B:	44.27		2745.		
MAX C:	35.53			890.	
D:	20.24				1827.
ROOT MEAN SQUARE		9.45	9.18	16.06	24.37
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	3	1	3	2
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 46.0 KSI
 ULT. STRENGTH: 62.0 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: RI003

ALUM.
ALLOY

2219

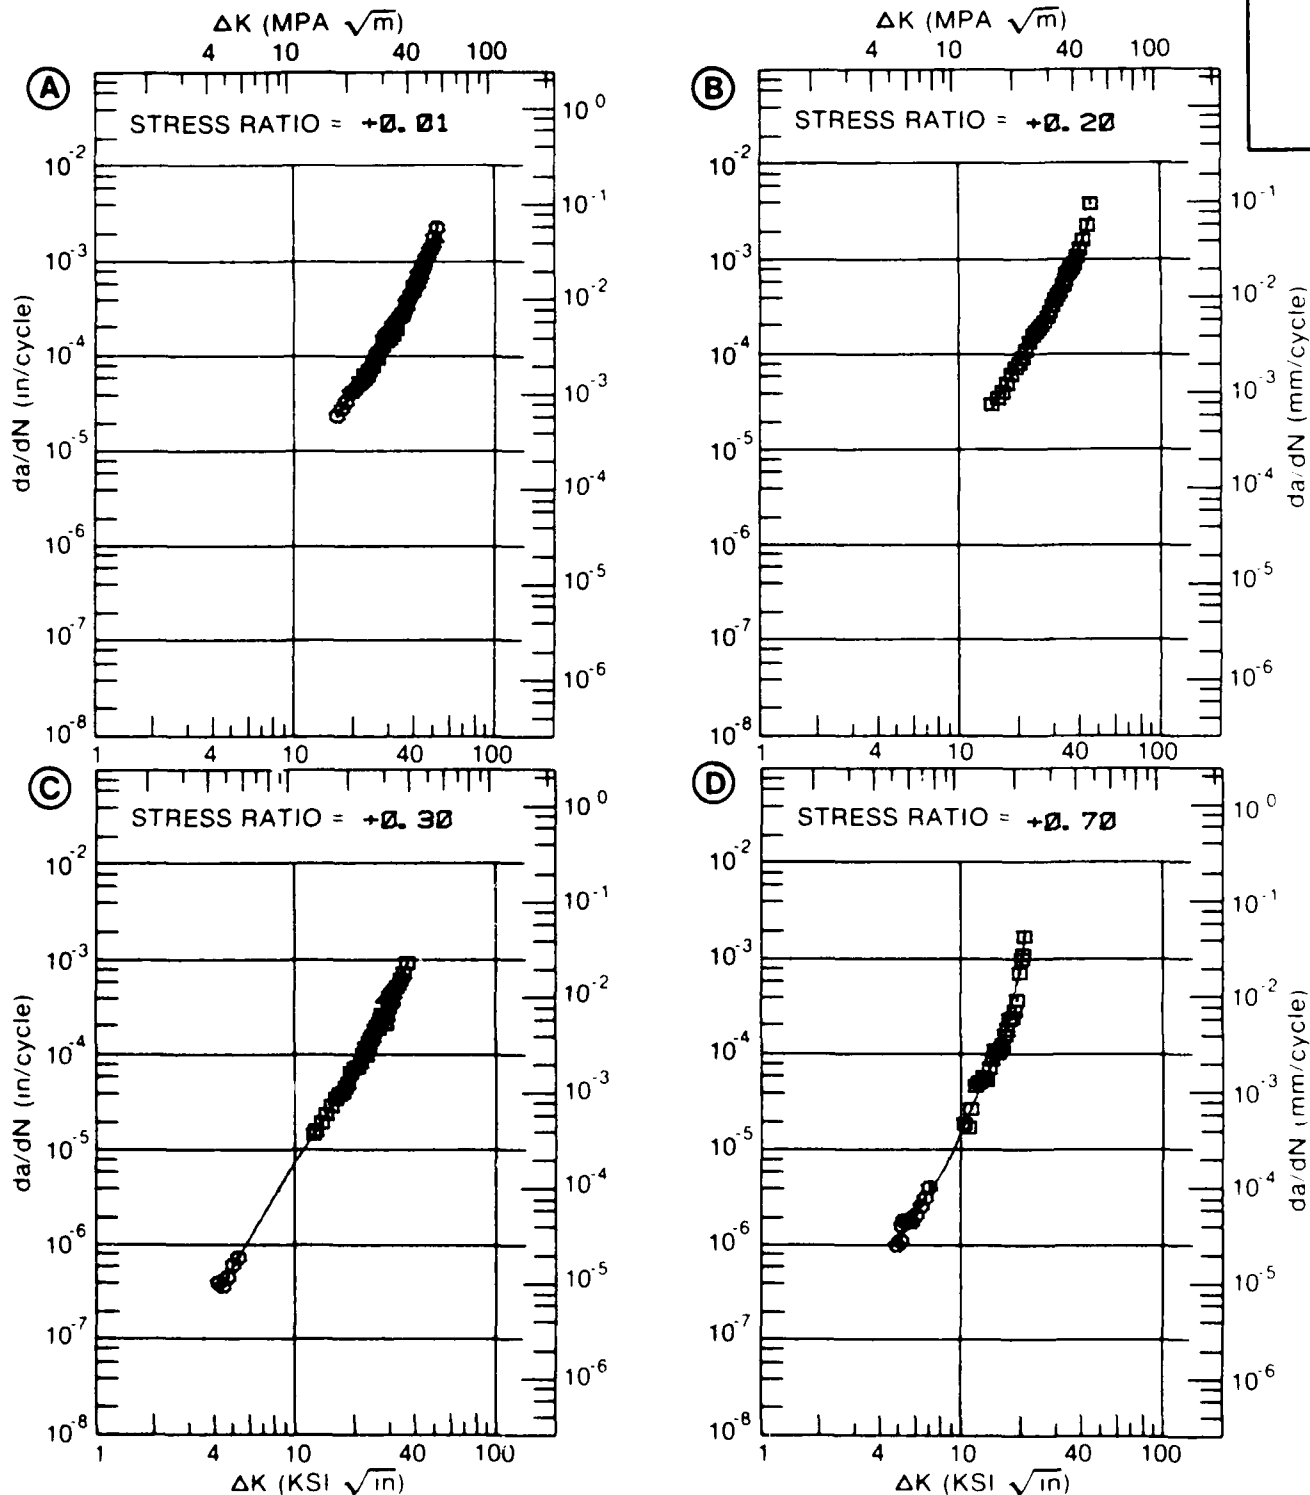


Figure 7.10.3.6

TABLE 7.10.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.7 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
A:	14.80	15.1			
DELTA K B:					
MIN C:					
D:					
	16.00	20.5			
	20.00	44.5			
	25.00	89.9			
	30.00	163.			
	35.00	287.			
	40.00	505.			
	50.00	1622.			
A:	52.25	2126.			
DELTA K B:					
MAX C:					
D:					
ROOT MEAN SQUARE		10.58			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 0.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.01
 FREQUENCY: 3.00 HZ

YIELD STRENGTH: 46.0 KSI
 ULT. STRENGTH: 62.0 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: RI003

ALUM.
ALLOY

2219

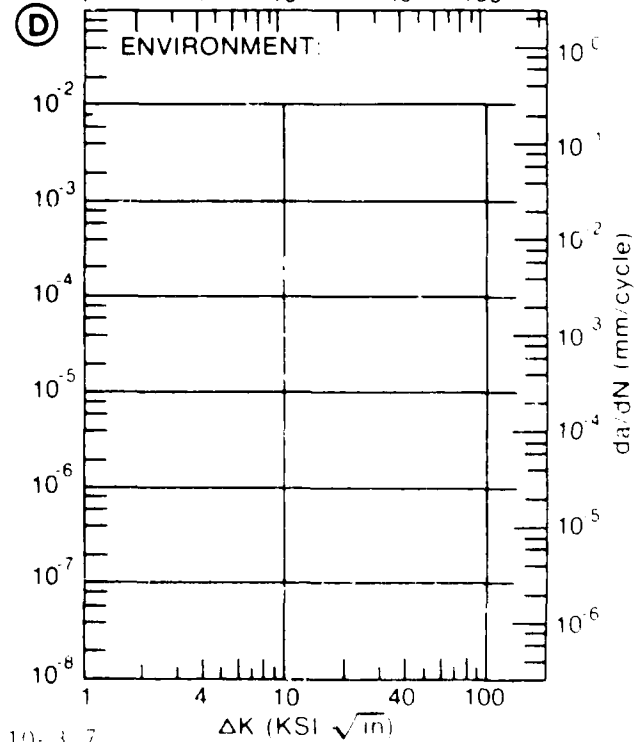
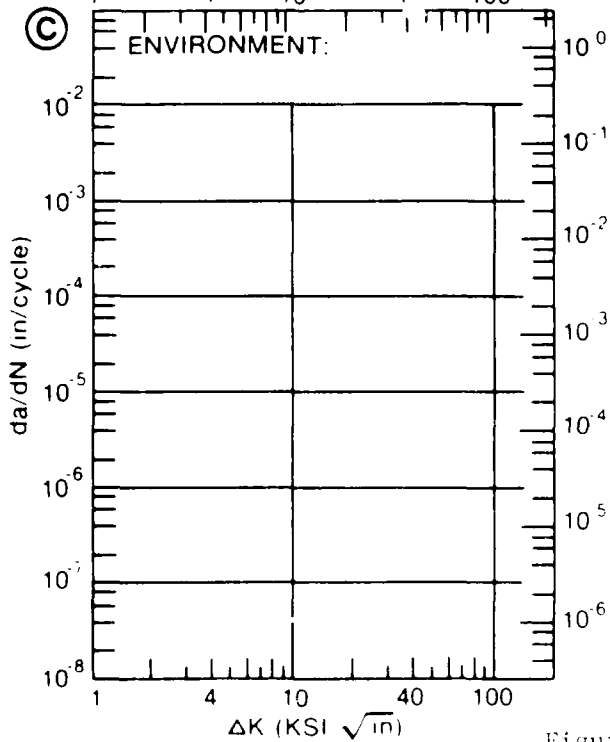
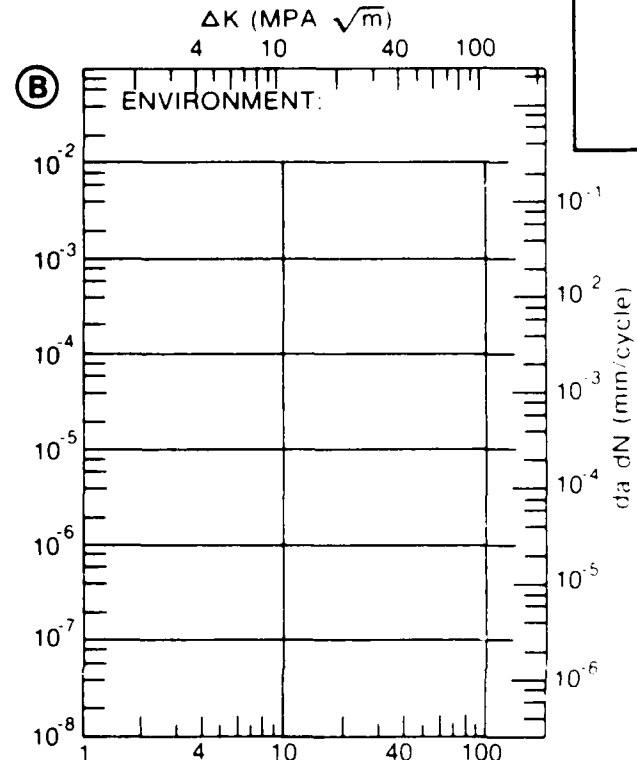
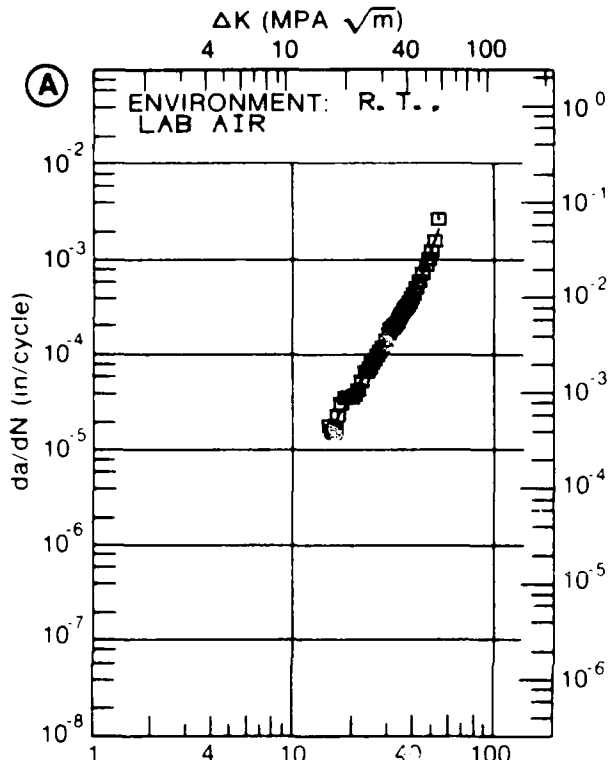


Figure 7.10-3.7

TABLE 7.10.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.8 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-0.10	R=+0.05	R=+0.10	
DELTA K	A: 25.44	90.5			
MIN	B: 8.91		3.55		
	C: 16.46			18.8	
	D:				
	9.00		3.67		
	10.00		5.14		
	13.00		11.5		
	16.00		22.1		
	20.00		48.3	44.9	
	25.00		120.	81.0	
	30.00	230.	185.		
DELTA K	A: 33.66	620.			
MAX	B: 30.18		184.		
	C: 28.06			212.	
	D:				
ROOT MEAN SQUARE		23.46	21.47	27.02	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8			1	
RATIO	0.8-1.25		1		
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 0.83" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00- 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 54.7 KSI
 ULT. STRENGTH: 66.9 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: 88468

ALUM.
ALLOY

2219

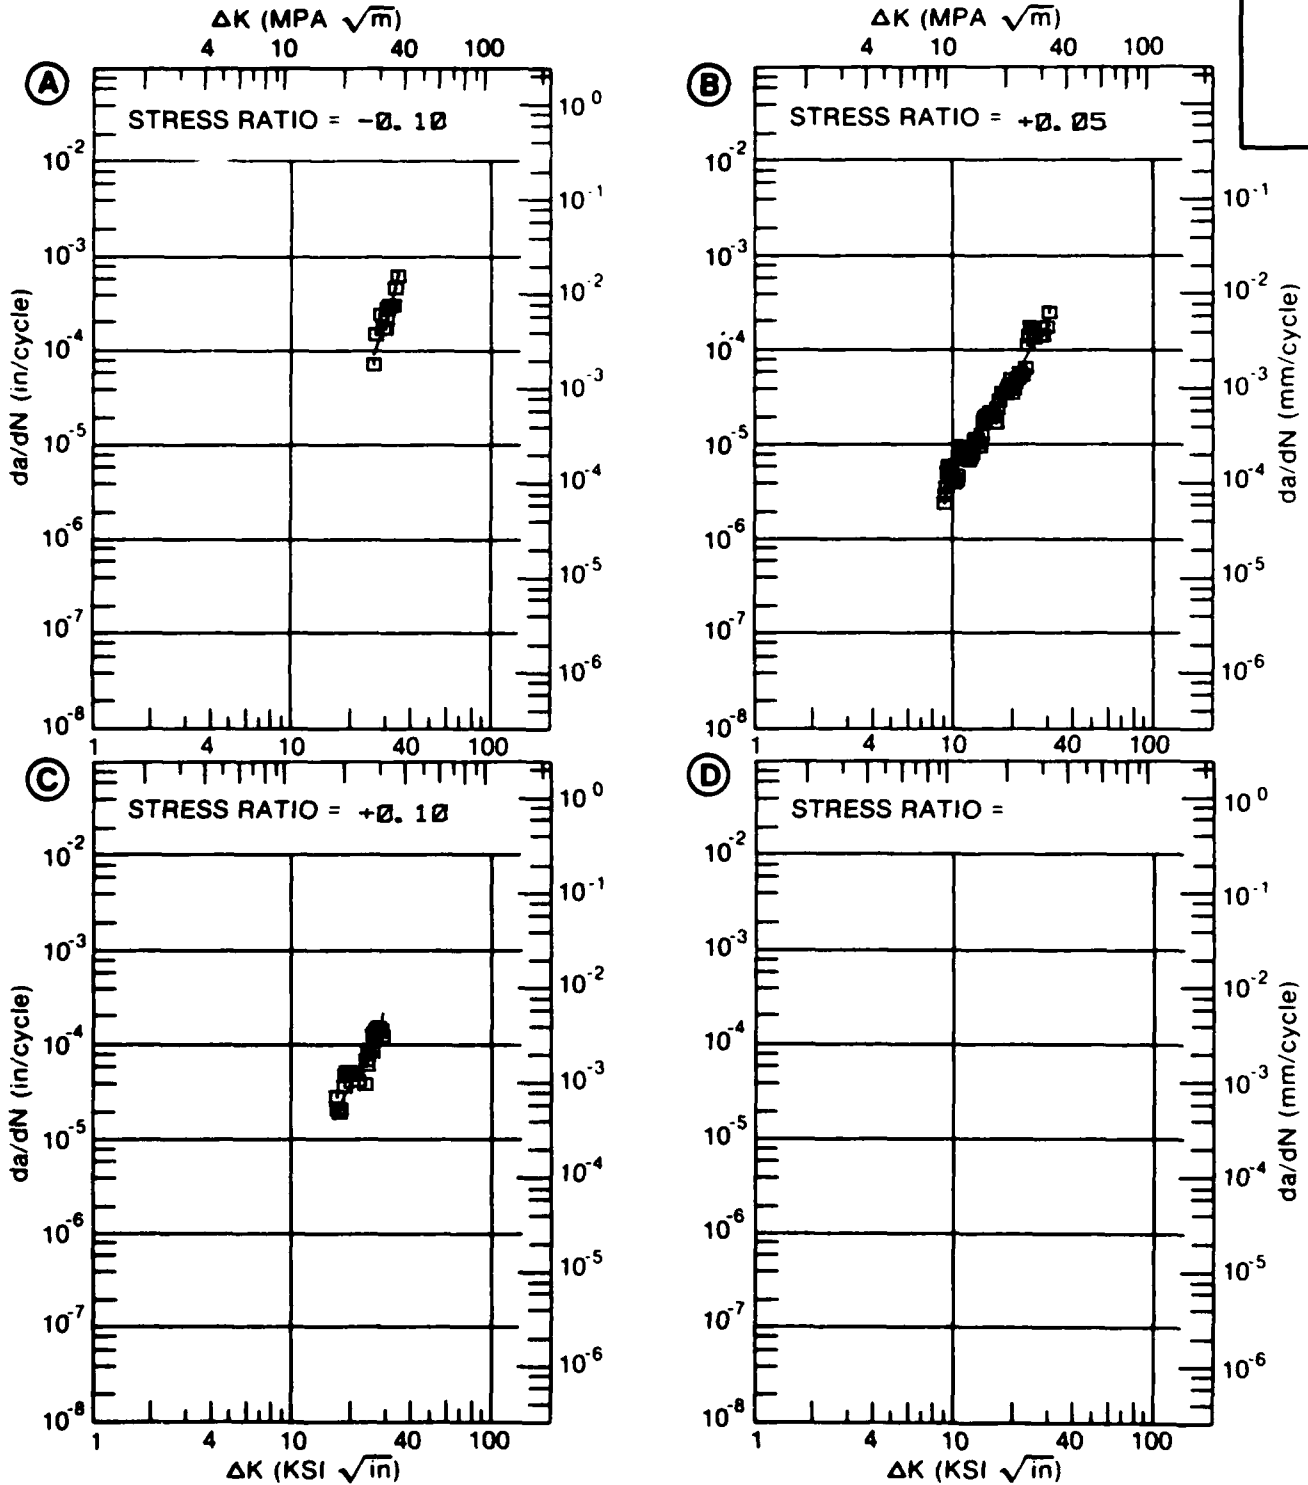


Figure 7.10-3.8

TABLE 7.10+3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.9 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-1.00	R=+0.04	R=+0.05	R=+0.30
DELTA K MIN	A: 7.34	1.68			
	B: 7.42		.41		
	C: 8.55			.79	
	D:				
	8.00	2.50	1.01		
	9.00	4.04	2.57	1.18	
	10.00	5.92	4.24	2.46	
	13.00	13.6		9.40	
	16.00	25.2		19.1	
	20.00	52.3		33.9	
	25.00			57.6	
	30.00			95.9	
DELTA K MAX	A: 24.44	116.			
	B: 11.28		7.87		
	C: 33.48			140.	
	D:				
ROOT MEAN SQUARE		16.15	12.09	29.69	0.00
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8	1	1	1	
	0.8-1.25			1	
	1.25-2.0				
	>2.0				

CONDITION/HT: T851
 FORM: 0.63" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00- 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 54.7 KSI
 ULT. STRENGTH: 66.9 KSI
 SPECIMEN THK: 0.250- 0.251"
 SPECIMEN WIDTH: 6.005- 6.070"
 REFERENCES: 89468

ALUM.
ALLOY

2219

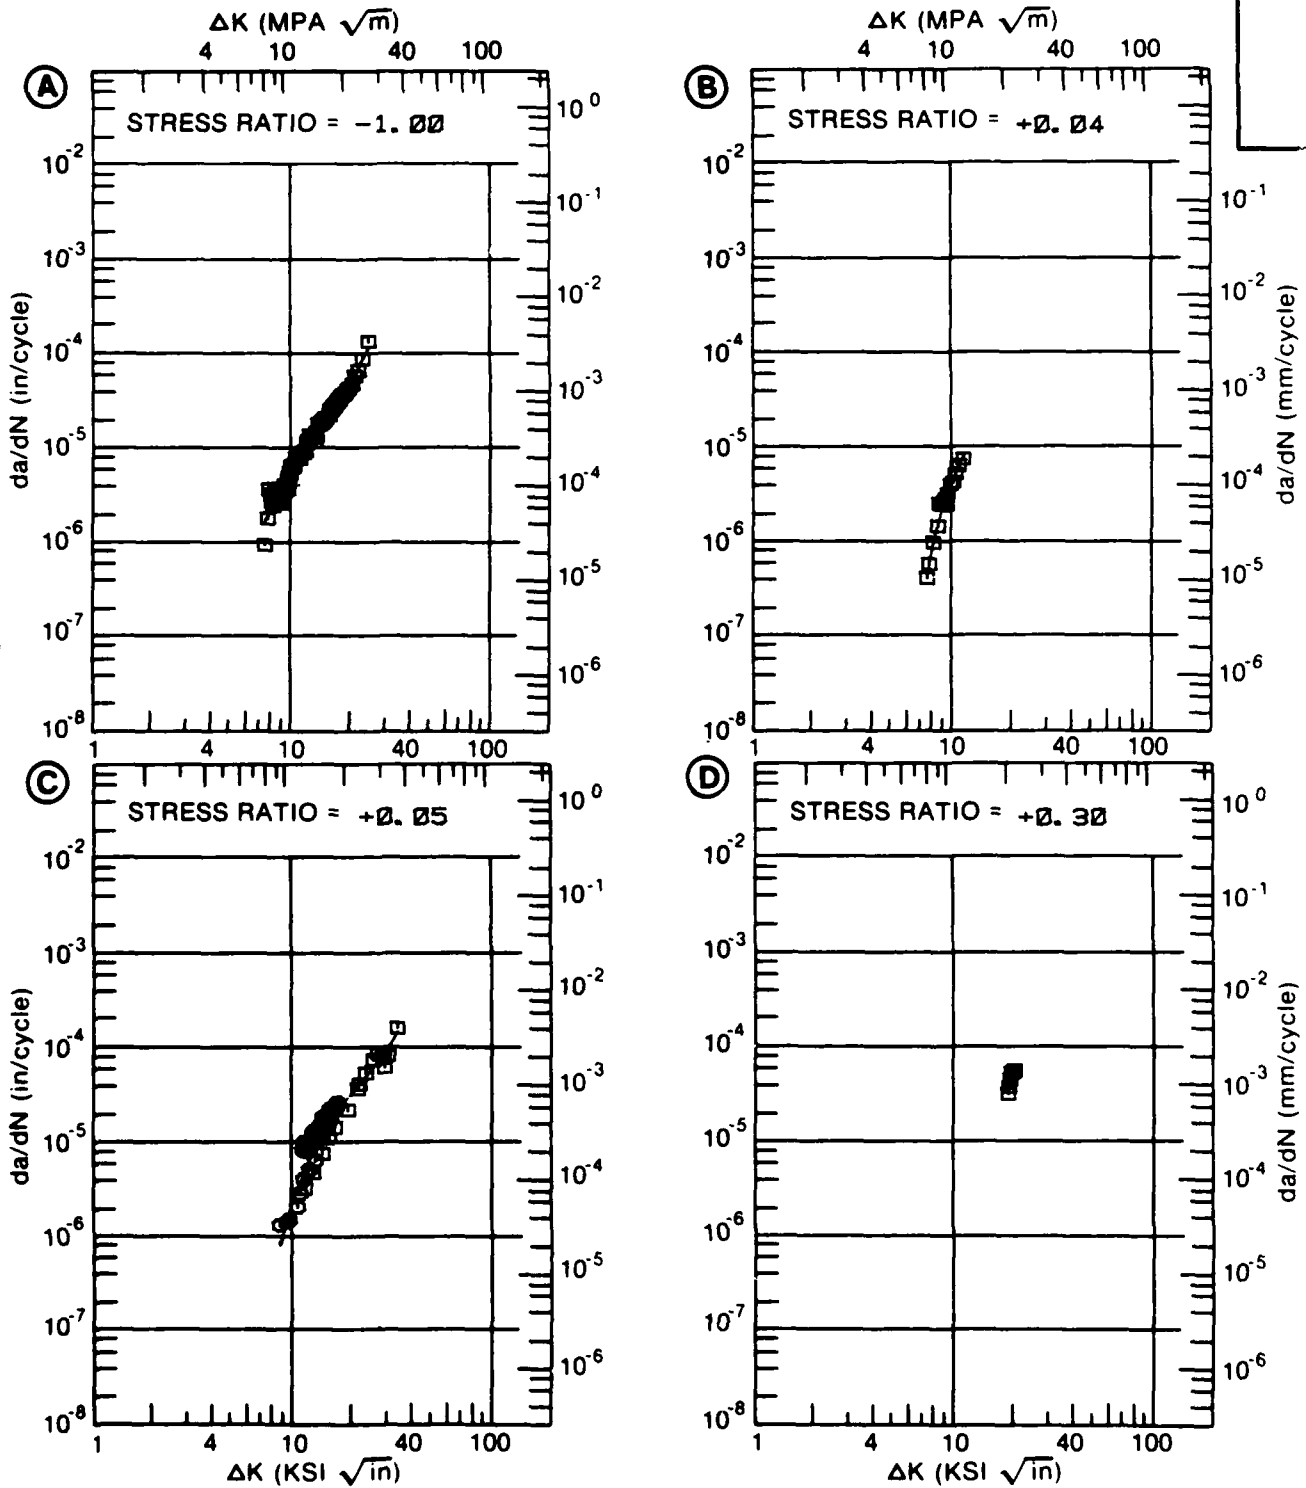


Figure 7.10.3.9

TABLE 7.10.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.10 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219
CONDITION: T851
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.05			
DELTA K MIN	A: 9.79	3.55			
	B:				
	C:				
	D:				
	10.00	3.58			
	13.00	13.2			
DELTA K MAX	A: 15.96	77.1			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 43.42
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION RATIO	0.5-0.8	1
SUMMARY (NP/NA)	0.8-1.25	
	1.25-2.0	
	>2.0	

CONDITION/HT: T851
 FORM: 0.63" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00- 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 54.7 KSI
 ULT. STRENGTH: 66.9 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: 88468

ALUM.
ALLOY

2219

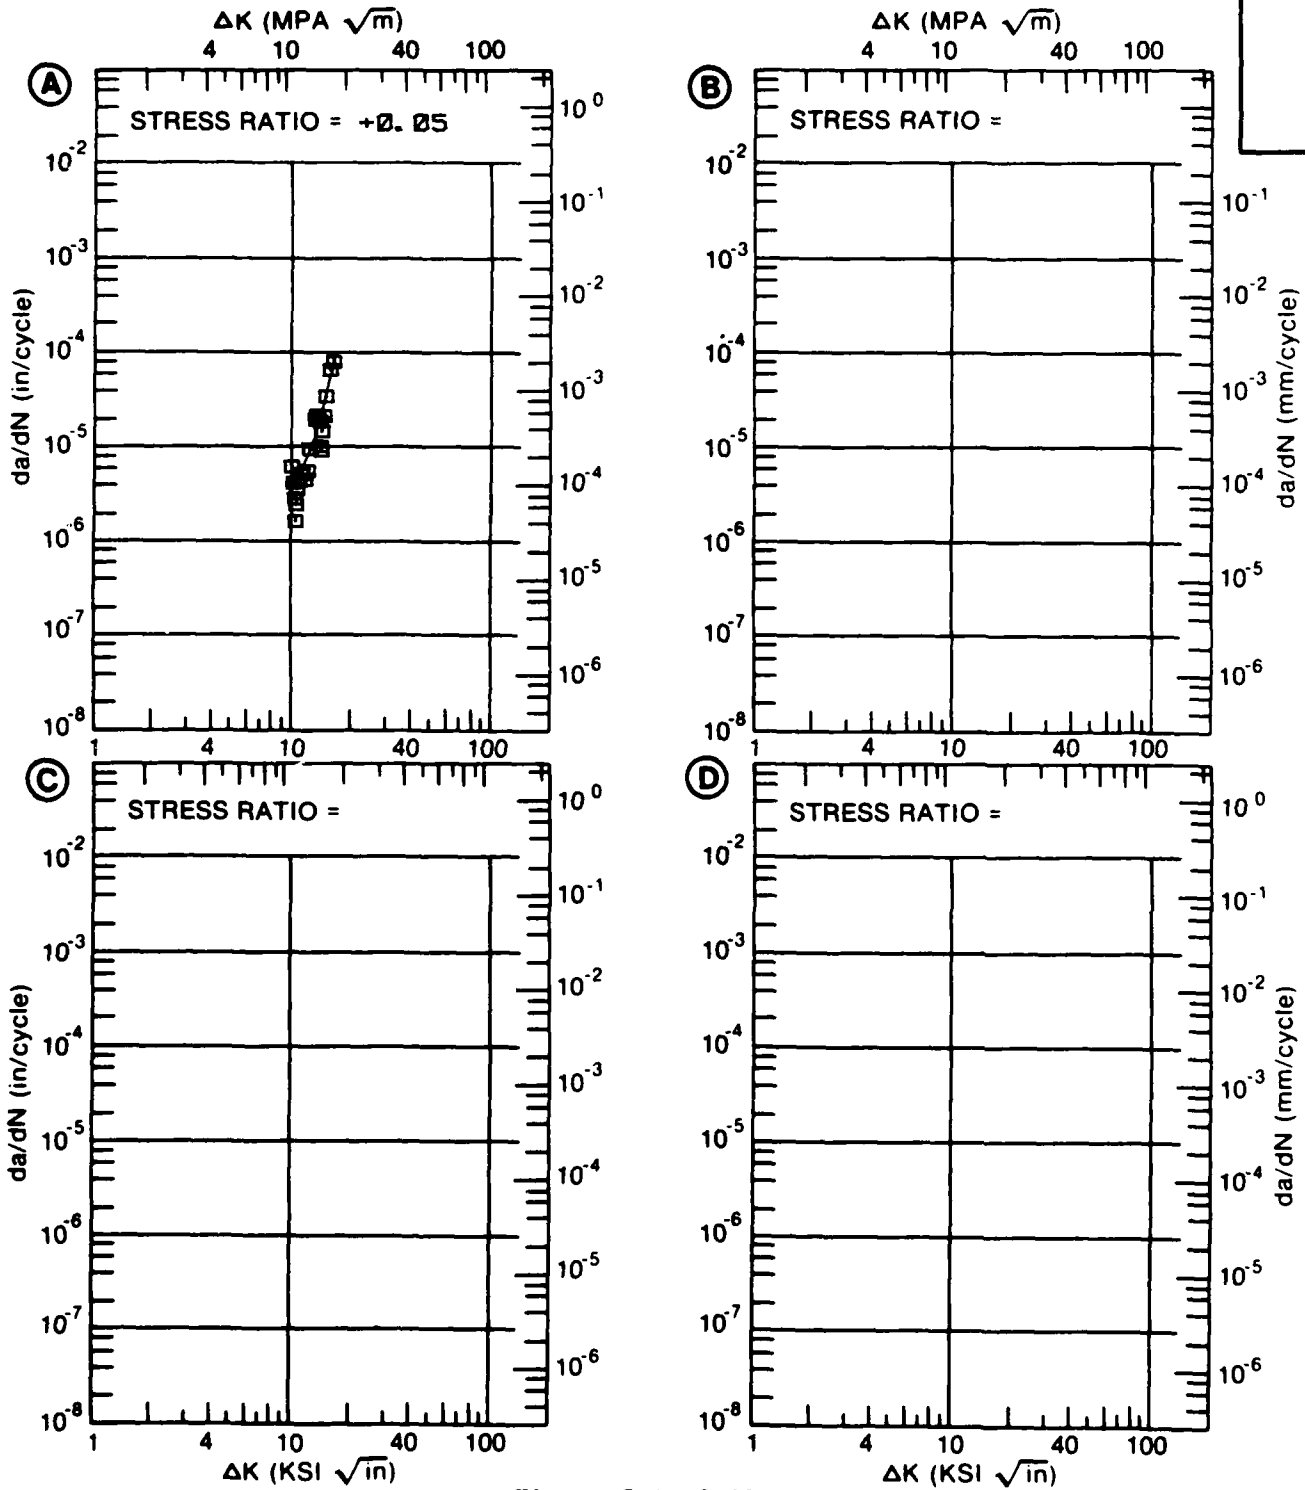


Figure 7.10.3.10

TABLE 7.10.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.11 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0. 40	R=+0. 50	R=+0. 60	R=+0. 70
DELTA K	A: 13. 87 :	28. 6			
MIN	B: 8. 00 :		4. 62		
	C: 7. 23 :			4. 35	
	D: 6. 44 :				3. 55
	7. 00 :				3. 79
	8. 00 :		4. 62	6. 09	6. 31
	9. 00 :		6. 15	8. 72	11. 6
	10. 00 :		10. 1	12. 2	
	13. 00 :			36. 9	
DELTA K	A: 15. 45 :	44. 3			
MAX	B: 10. 28 :		10. 6		
	C: 14. 98 :			91. 8	
	D: 9. 77 :				16. 7
ROOT MEAN SQUARE		17. 15	10. 21	24. 18	13. 13
PERCENT ERROR					
LIFE	0. 0-0. 5				
PREDICTION	0. 5-0. 8				
RATIO	0. 8-1. 25	1	1	1	1
SUMMARY	1. 25-2. 0				
(NP/NA)	>2. 0				

CONDITION/HT: T851
 FORM: 0.63" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 1.00- 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 54.7 KSI
 ULT. STRENGTH: 66.9 KSI
 SPECIMEN THK: 0.250- 0.251"
 SPECIMEN WIDTH: 6.005- 6.070"
 REFERENCES: 88468

ALUM.
 ALLOY
 2219

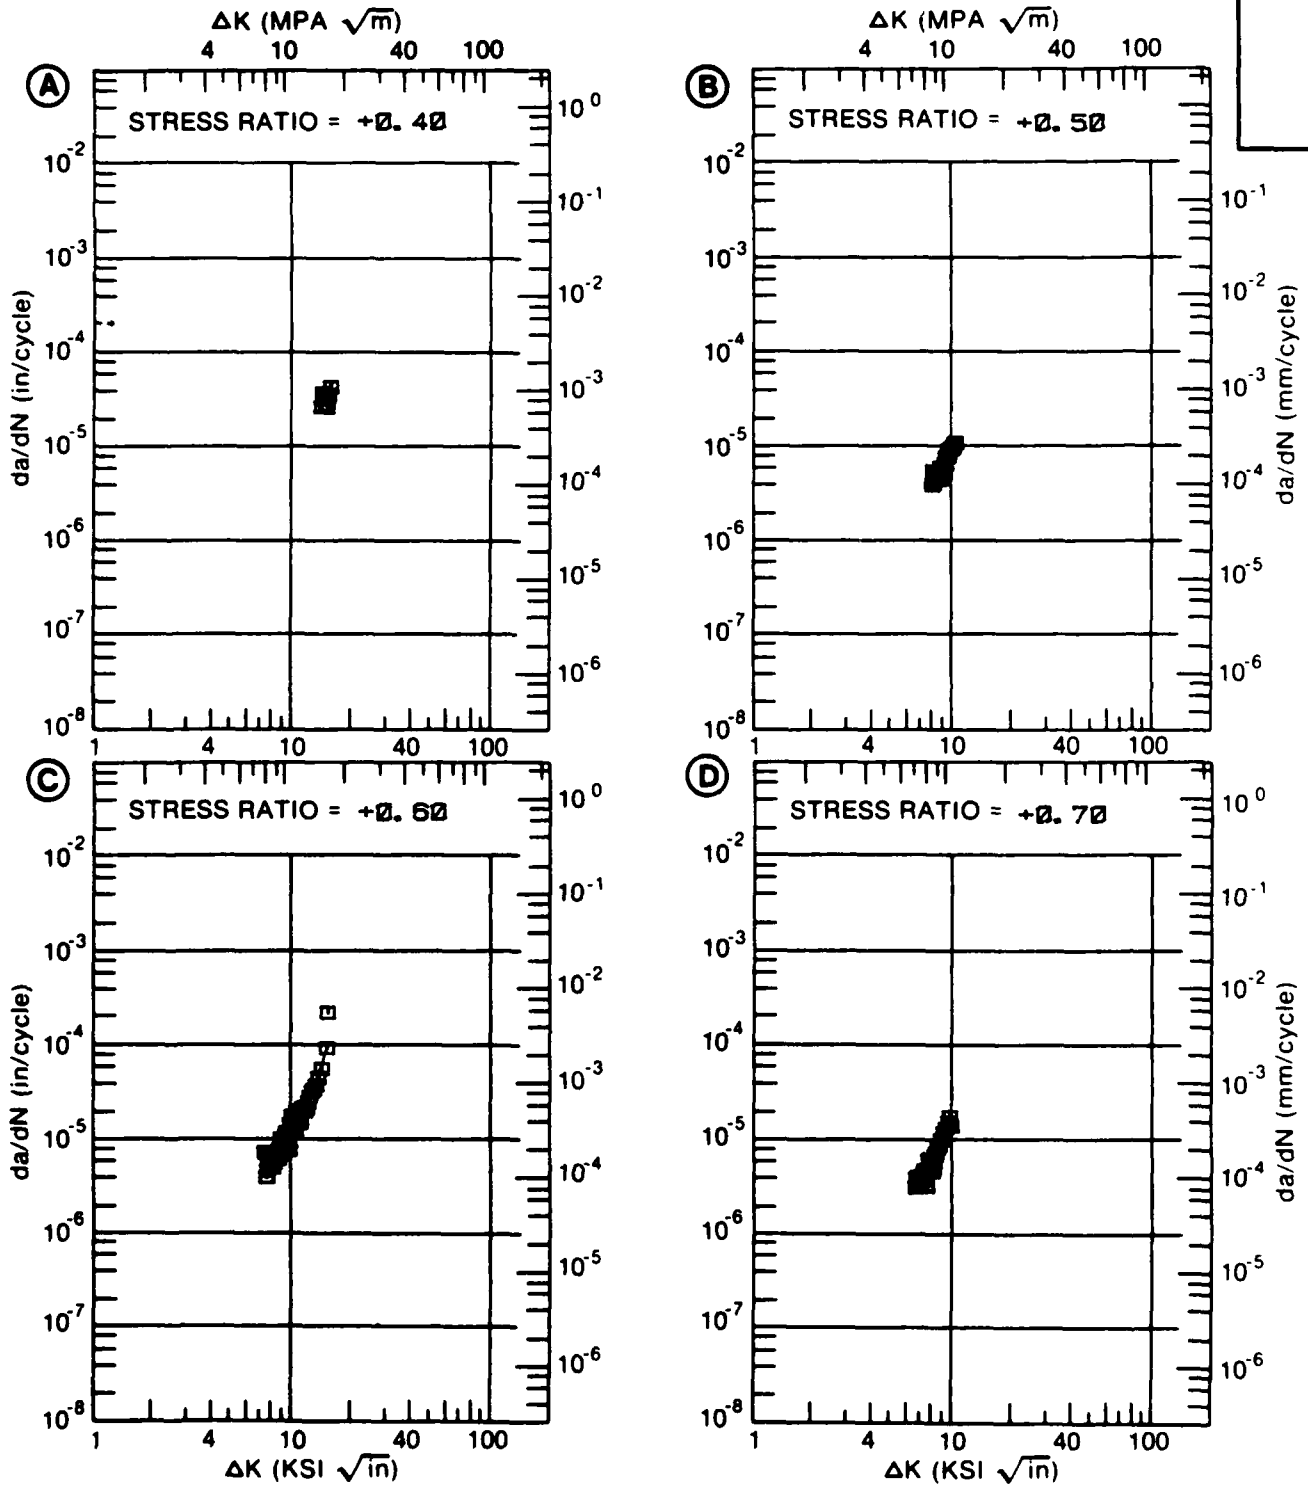


Figure 7.10.3.11

TABLE 7.10.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.12 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , LAB AIR					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=-0.50	R=+0.00		
DELTA K MIN	A: 5.96	1.53			
	B: 5.21		.360		
	C:				
	D:				
	6.00	1.59	1.22		
	7.00	3.08	2.67		
	8.00	4.48	4.19		
	9.00	5.71	6.02		
	10.00	6.89	8.25		
	13.00	12.6	17.5		
	16.00		30.8		
	20.00		54.8		
DELTA K MAX	A: 15.70	28.1			
	B: 20.85		60.8		
	C:				
	D:				
ROOT MEAN SQUARE		19.95	9.86		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8	1			
	0.8-1.25	3	6		
	1.25-2.0				
	>2.0				

CONDITION/HT: T851
 FORM: 1.38" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 5.20 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 50.6 KSI
 ULT. STRENGTH: 66.4 KSI
 SPECIMEN THK: 0.748- 0.752"
 SPECIMEN WIDTH: 2.997- 3.003"
 REFERENCES: 96213

ALUM. ALLOY
2219

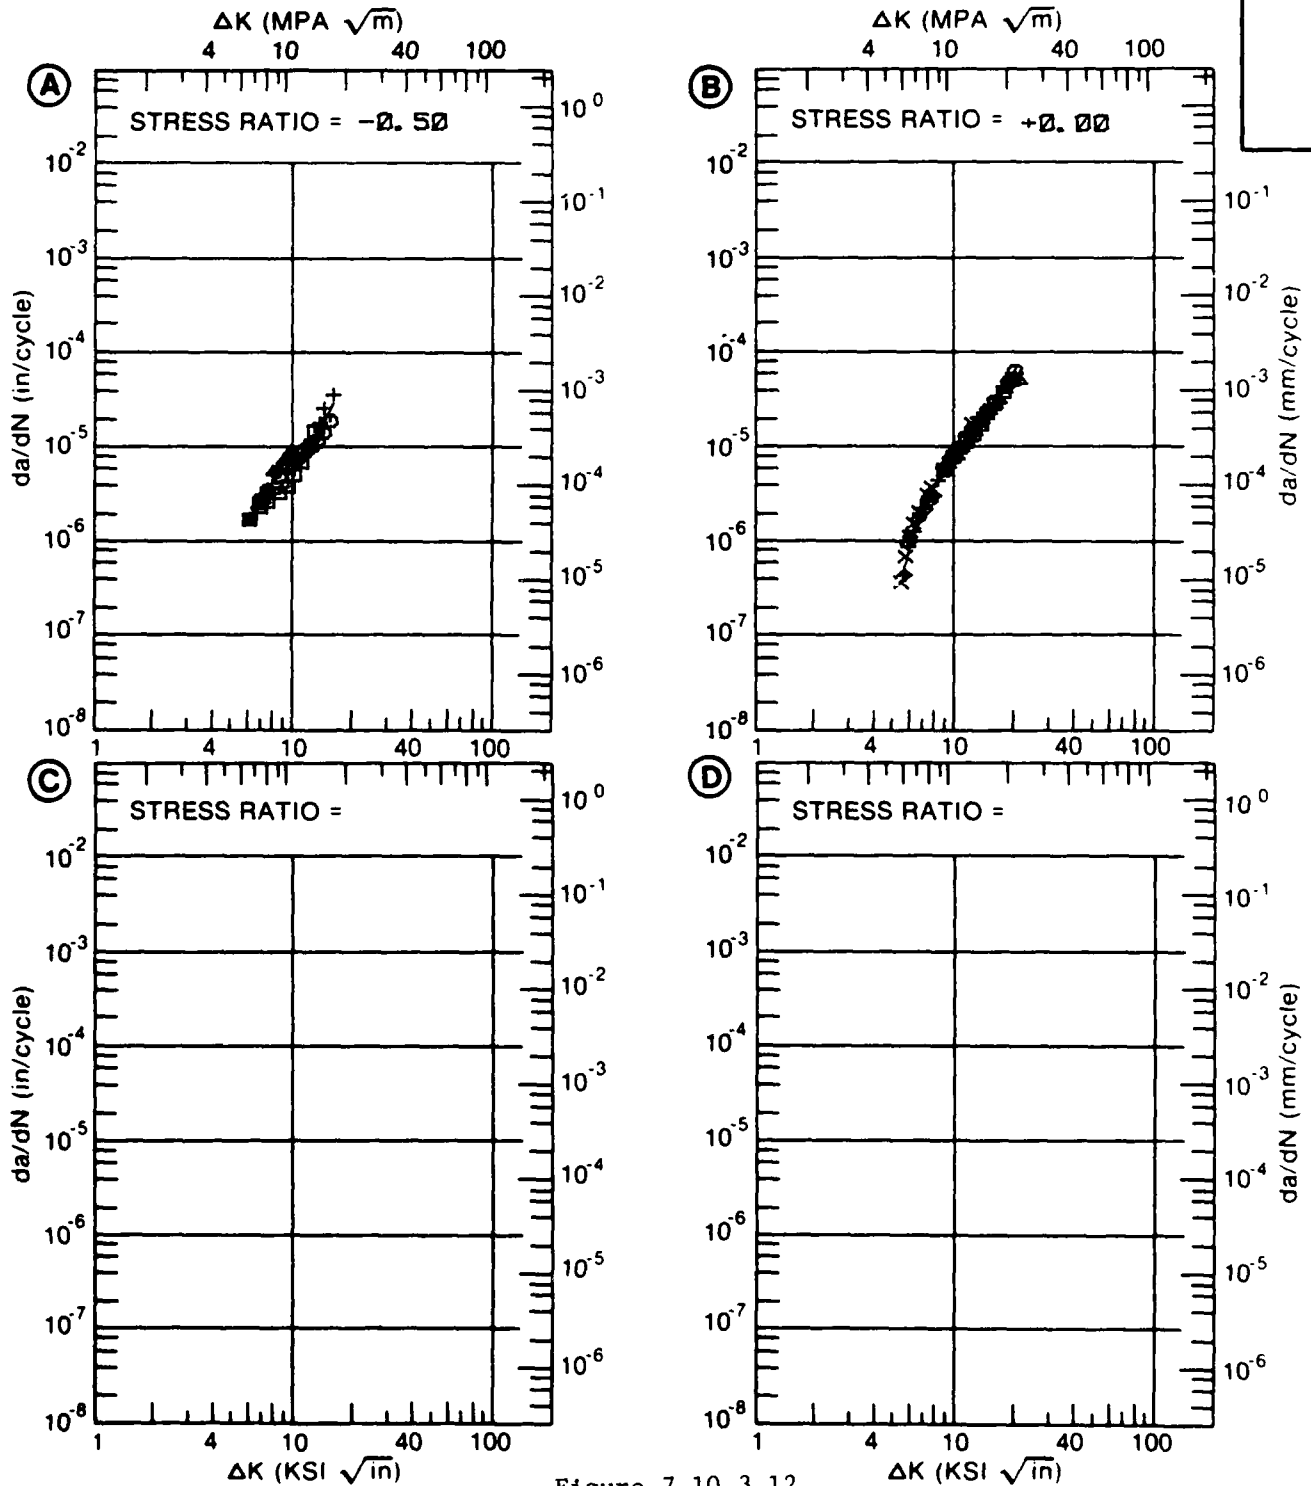


Figure 7.10.3.12

TABLE 7.10.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.13 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN. /CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30		
DELTA K MIN	A: 3.83	.232			
	B: 4.70		.673		
	C:				
	D:				
	4.00	.243			
	5.00	.407	.907		
	6.00	.779	1.84		
	7.00	1.40	3.11		
	8.00	2.25	5.19		
	9.00	3.36	9.20		
	10.00	4.77			
	13.00	11.2			
	16.00	22.6			
DELTA K MAX	A: 16.51	25.2			
	B: 9.78		15.2		
	C:				
	D:				
ROOT MEAN SQUARE		9.44	7.15		
PERCENT ERROR					
LIFE PREDICTION	0.0-0.5				
RATIO SUMMARY	0.5-0.8				
(NP/NA)	0.8-1.25	1	1		
	1.25-2.0				
	>2.0				

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 48.0- 49.6 KSI
 ULT. STRENGTH: 65.9- 66.2 KSI
 SPECIMEN THK: 0.993- 1.000"
 SPECIMEN WIDTH: 6.010- 7.400"
 REFERENCES: 85837

ALUM.
ALLOY

2219

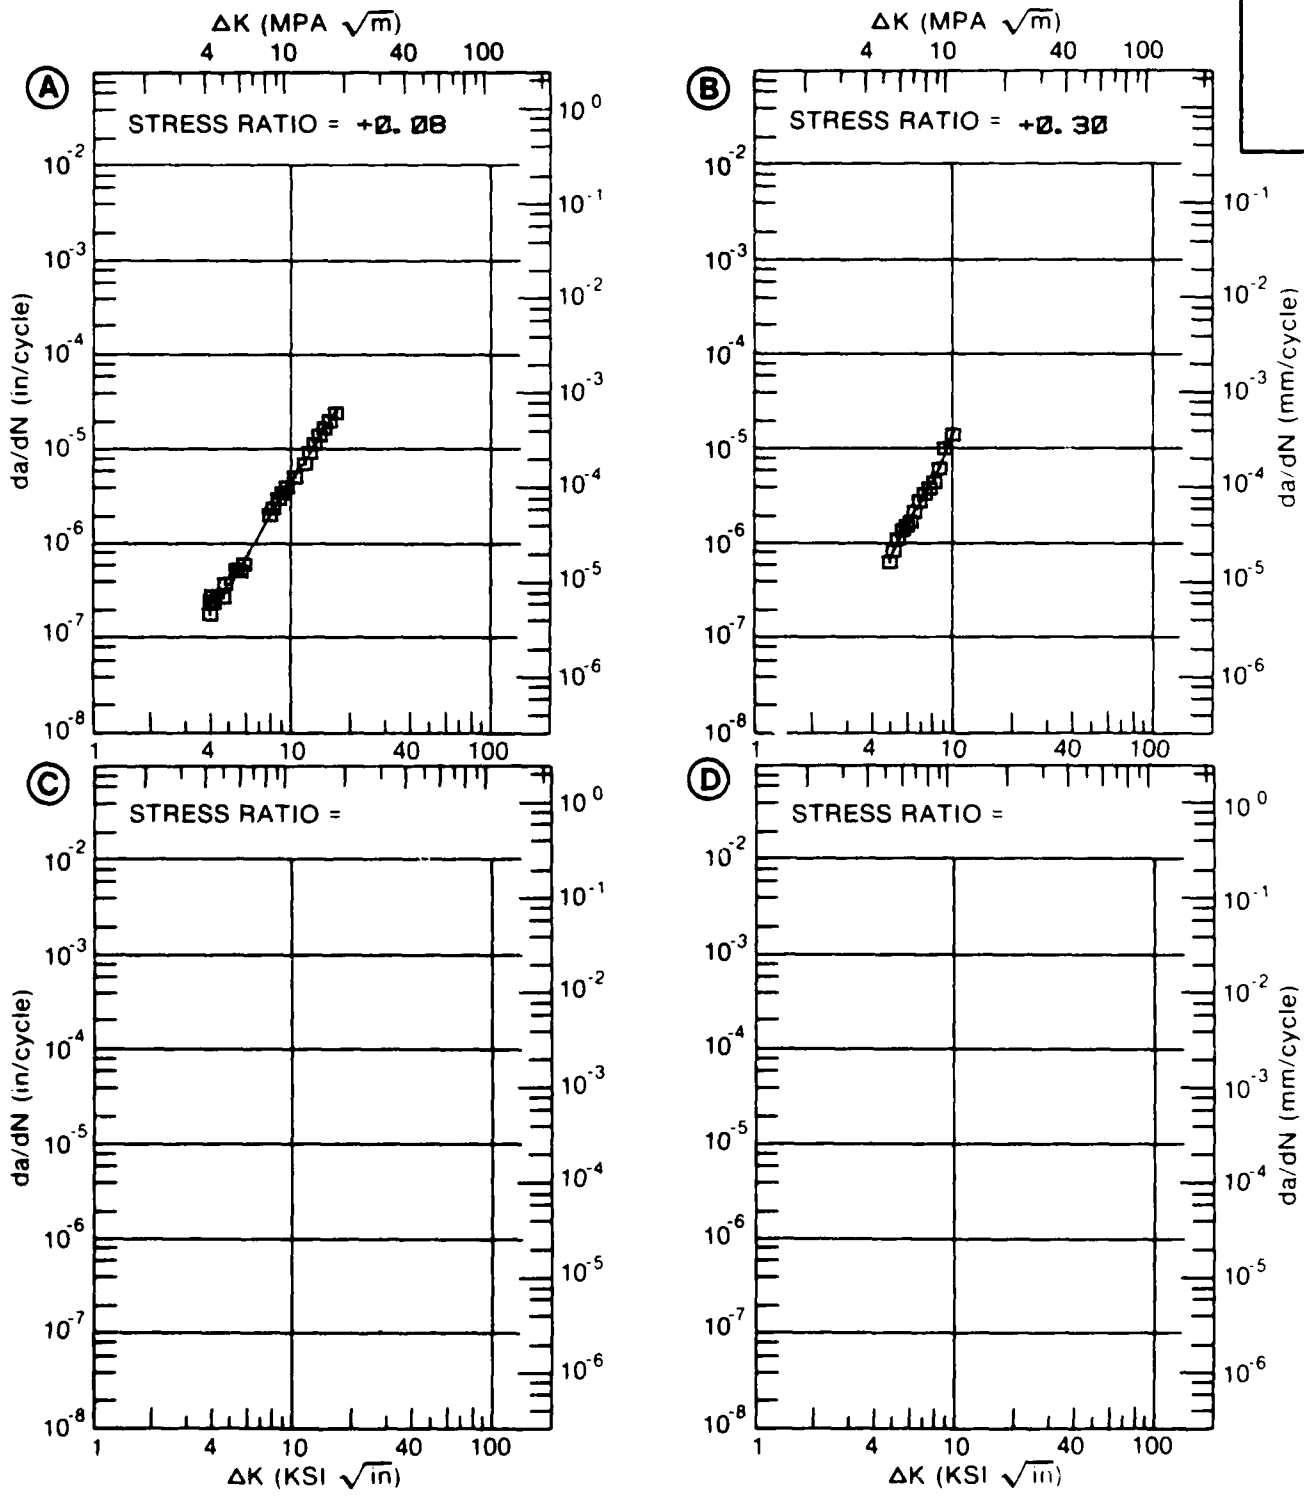


Figure 7.10.3.13

TABLE 7.10.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.14 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219
CONDITION: TB51
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	R=+0.08			
DELTA K A: 6.98	1.33			
MIN B:				
C:				
D:				
7.00	1.35			
8.00	2.41			
9.00	3.86			
10.00	5.74			
13.00	14.6			
DELTA K A: 15.01	24.3			
MAX B:				
C:				
D:				

ROOT MEAN SQUARE 6.99
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.995"
 SPECIMEN WIDTH: 2.000"
 REFERENCES: 85837

ALUM.
ALLOY

2219

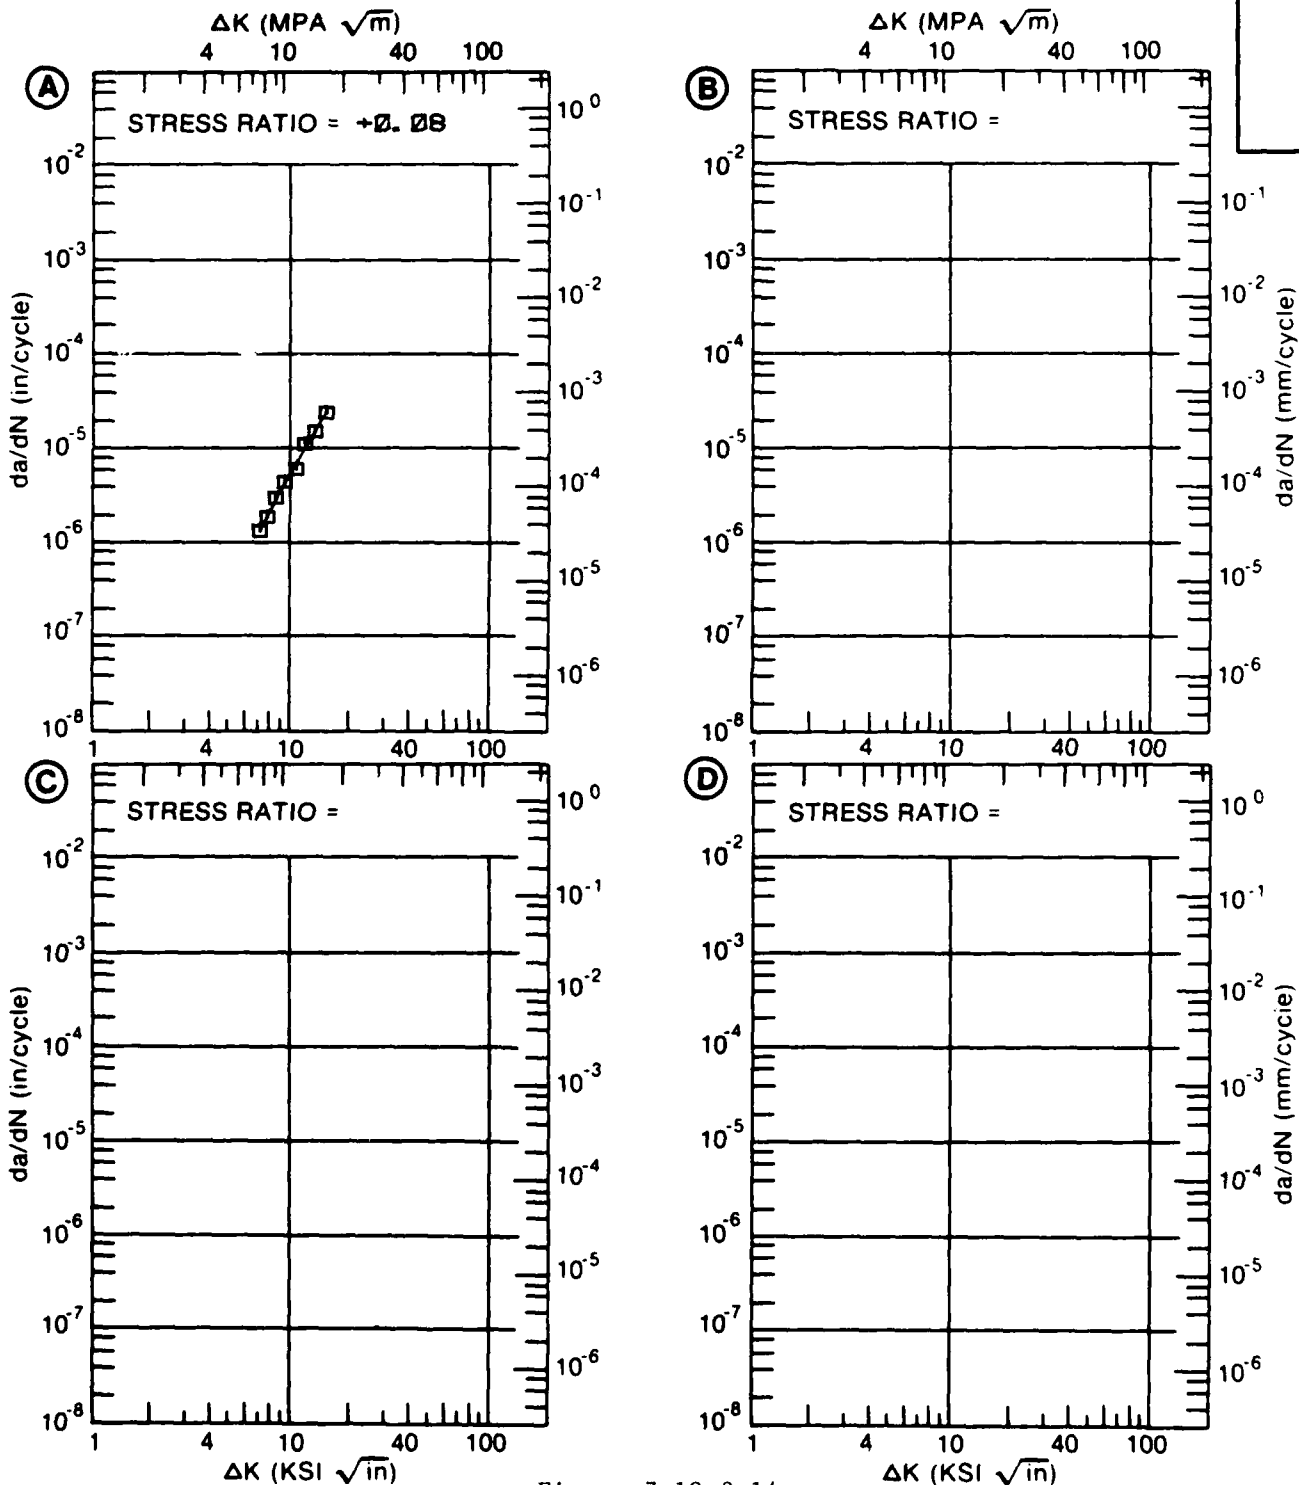


Figure 7.10.3.14

TABLE 7.10.3.15

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.15 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
ENVIRONMENT: R. T. , S. T. W.					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.30	R=+0.50		
DELTA K MIN	A: 5.54	.953			
	B: 4.67		.479		
	C:				
	D:				
	5.00		.809		
	6.00	1.33	2.09		
	7.00	2.46	3.88		
	8.00	4.04	6.06		
	9.00	6.10	8.62		
	10.00	8.68	11.6		
	13.00	19.7	25.1		
	16.00	35.7	53.6		
	20.00	65.6			
DELTA K MAX	A: 21.28	77.3			
	B: 16.41		59.7		
	C:				
	D:				
ROOT MEAN SQUARE		5.63	17.56		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0		1		

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 6.000- 6.010"
 REFERENCES: 98579

ALUM.
 ALLOY

2219

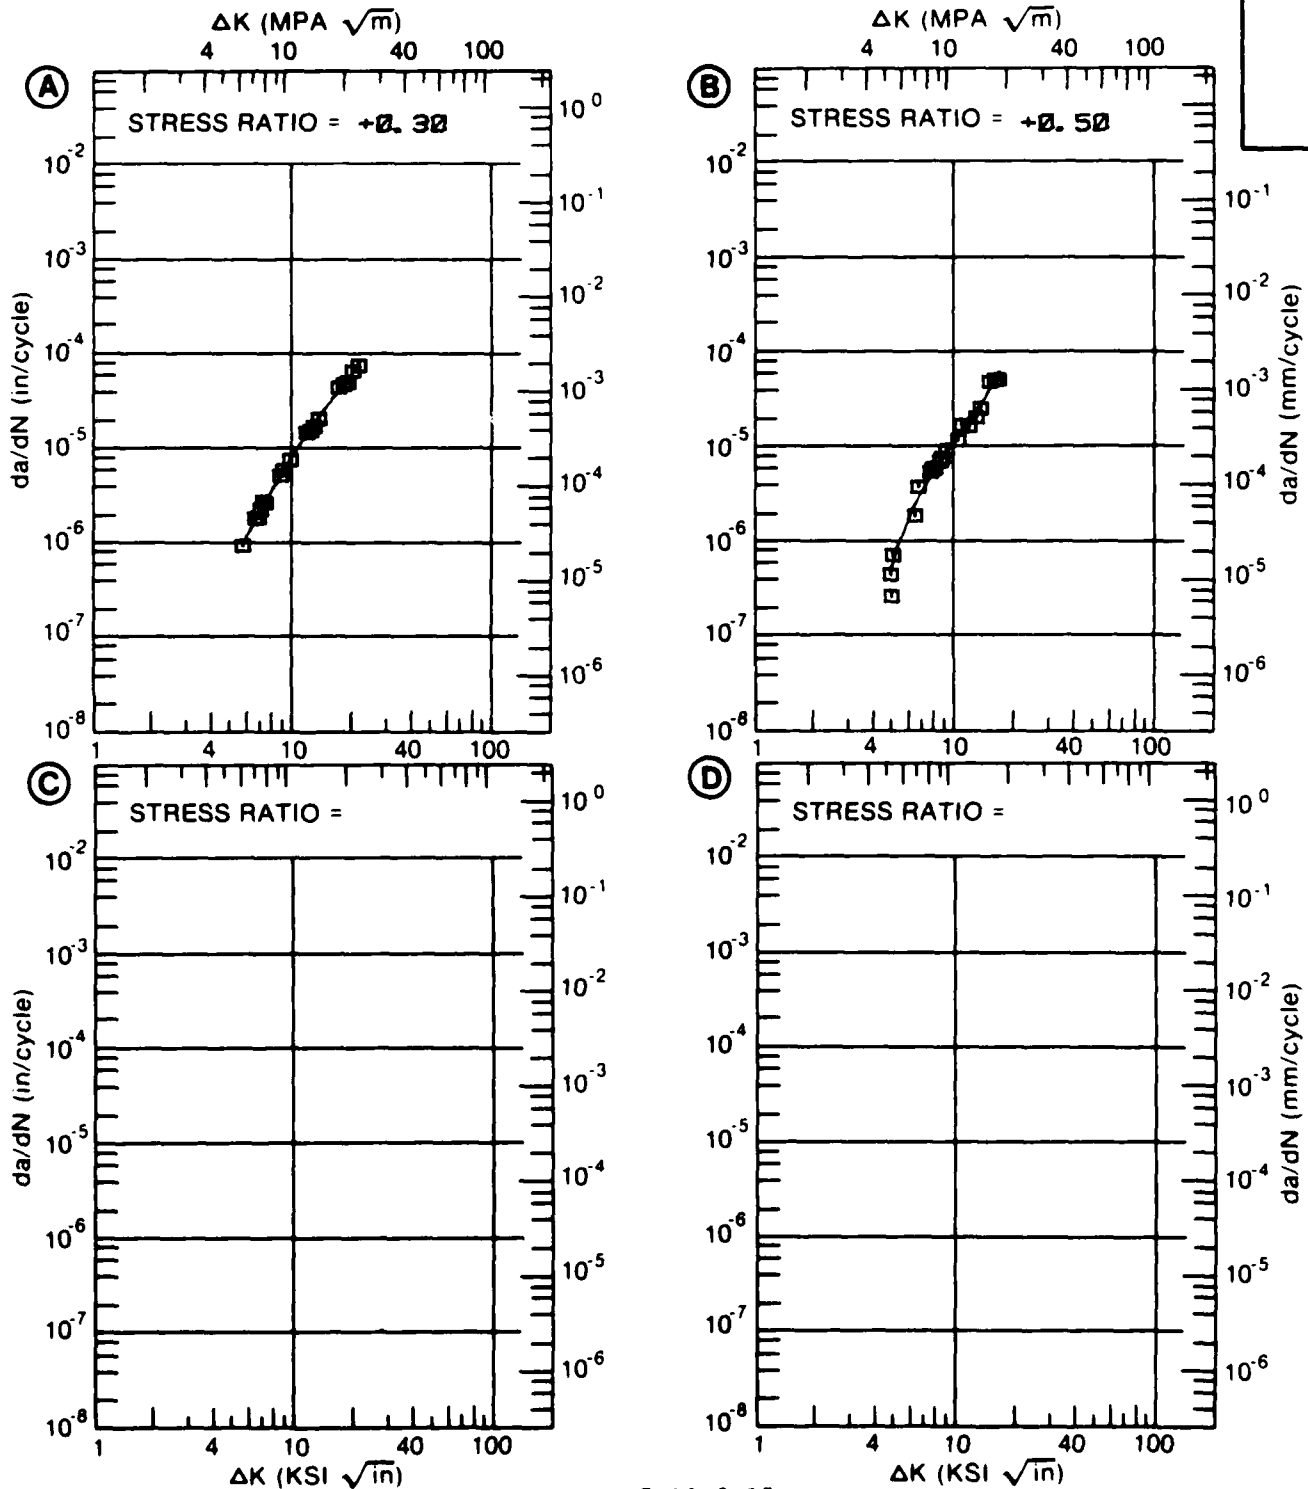


Figure 7.10.3.15

TABLE 7.10.3.16

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.16 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: TB51					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K	A: 6.84	.622			
MIN	B:				
	C:				
	D:				
	7.00	.708			
	8.00	1.40			
	9.00	2.34			
	10.00	3.52			
	13.00	8.20			
	16.00	14.5			
	20.00	26.5			
	25.00	51.9			
	30.00	100.			
	35.00	197.			
	40.00	393.			
DELTA K	A: 48.41	1306.			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		11.38			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.250- 0.500"
 SPECIMEN WIDTH: 5.990- 6.000"
 REFERENCES: 98579

ALUM.
ALLOY

2219

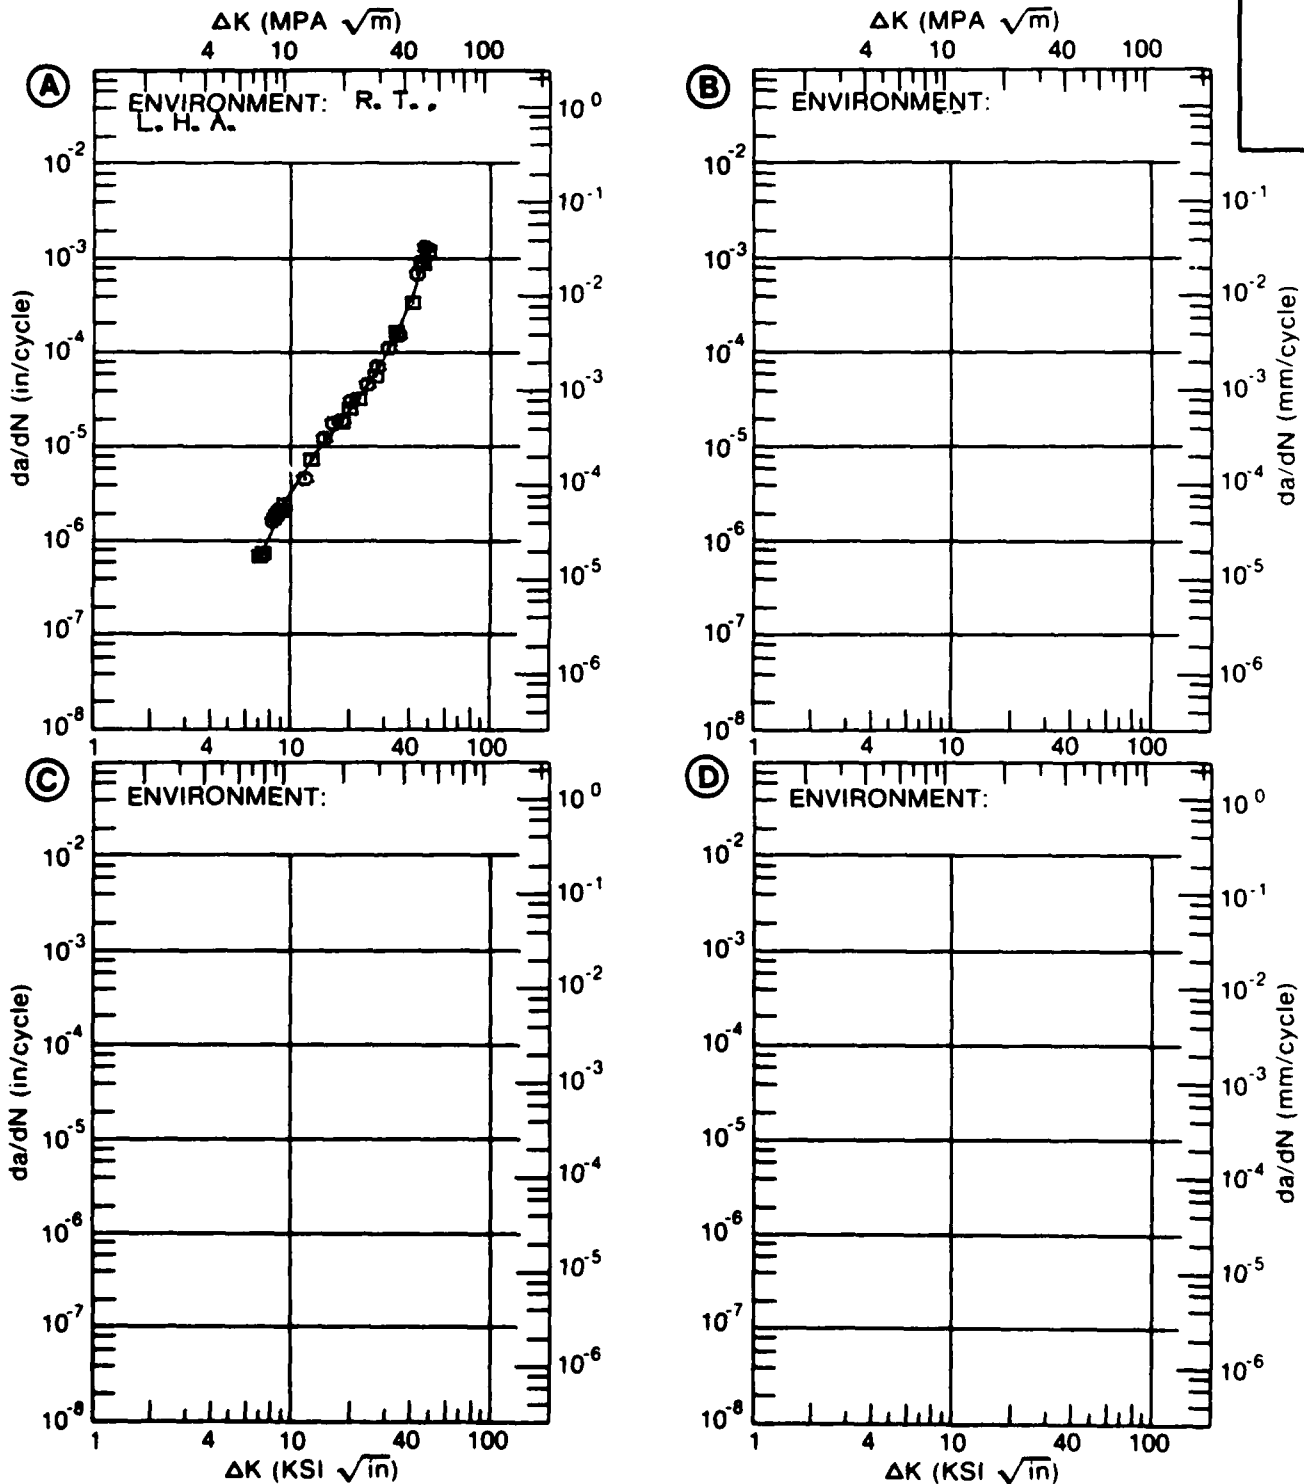


Figure 7.10.3.16

TABLE 7.10.3.17

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.17 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219
CONDITION: T851		
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)
		A B C D
		E=+ 265F
		L. H. A.
DELTA K MIN	A: 6.74	2.06
	B:	
	C:	
	D:	
	7.00	2.39
	8.00	3.94
	9.00	5.88
	10.00	8.22
	13.00	17.7
	16.00	31.4
	20.00	59.4
	25.00	120.
DELTA K MAX	A: 27.51	167.
	B:	
	C:	
	D:	
ROOT MEAN SQUARE PERCENT ERROR		6.40
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 86.0 KSI
 SPECIMEN THK: 0.990"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 88579

ALUM. ALLOY
2219

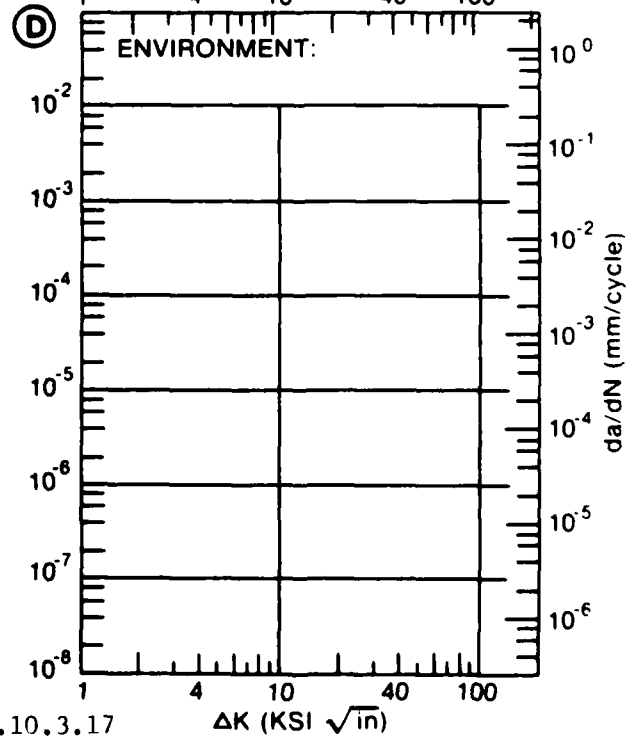
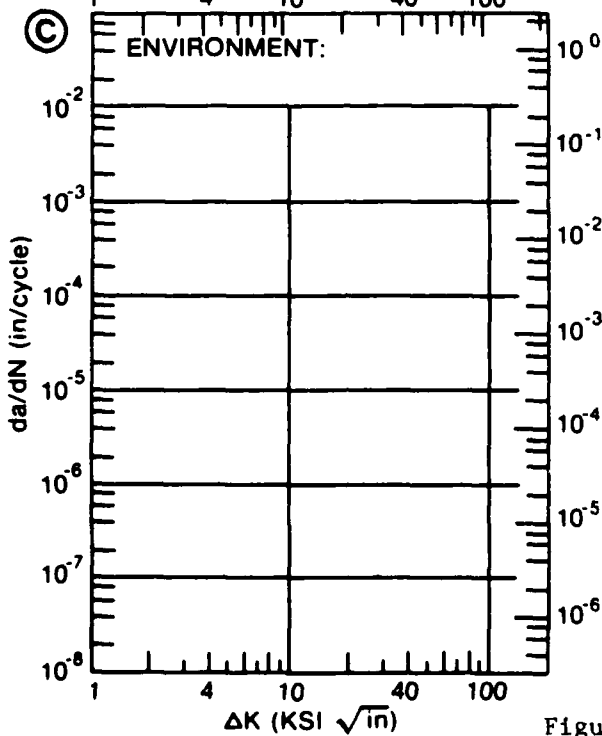
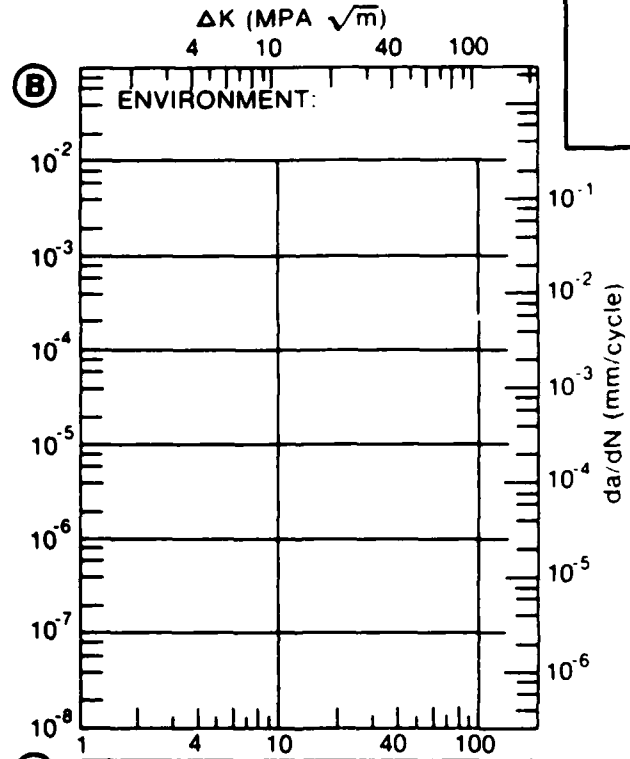
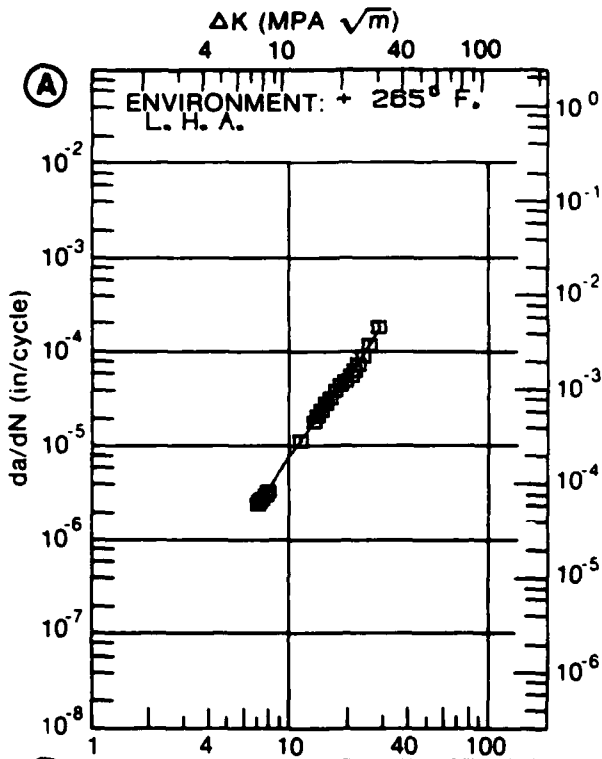


Figure 7.10.3.17

TABLE 7.10.3.18

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.18 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM
CONDITION: T851

2219

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. S. T. W.	E=+ 150F S. T. W.	
DELTA K MIN	A: 6.23	1.37			
	B: 4.99		.599		
	C: 6.17			2.57	
	D:				
	5.00		.605		
	6.00		1.41		
	7.00	2.57	2.52	3.76	
	8.00	4.43	4.08	6.90	
	9.00	6.40		11.5	
	10.00	8.48		15.3	
	13.00	17.7		18.8	
DELTA K MAX	A: 15.42	35.6			
	B: 8.98		6.46		
	C: 14.97			32.2	
	D:				

ROOT MEAN SQUARE PERCENT ERROR

	11.91	7.75	12.49
--	-------	------	-------

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1
---------------------------------------	--	---	---	---

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 49.6 KSI
 ULT. STRENGTH: 66.2 KSI
 SPECIMEN THK: 0.992- 0.998"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

ALUM.
ALLOY

2219

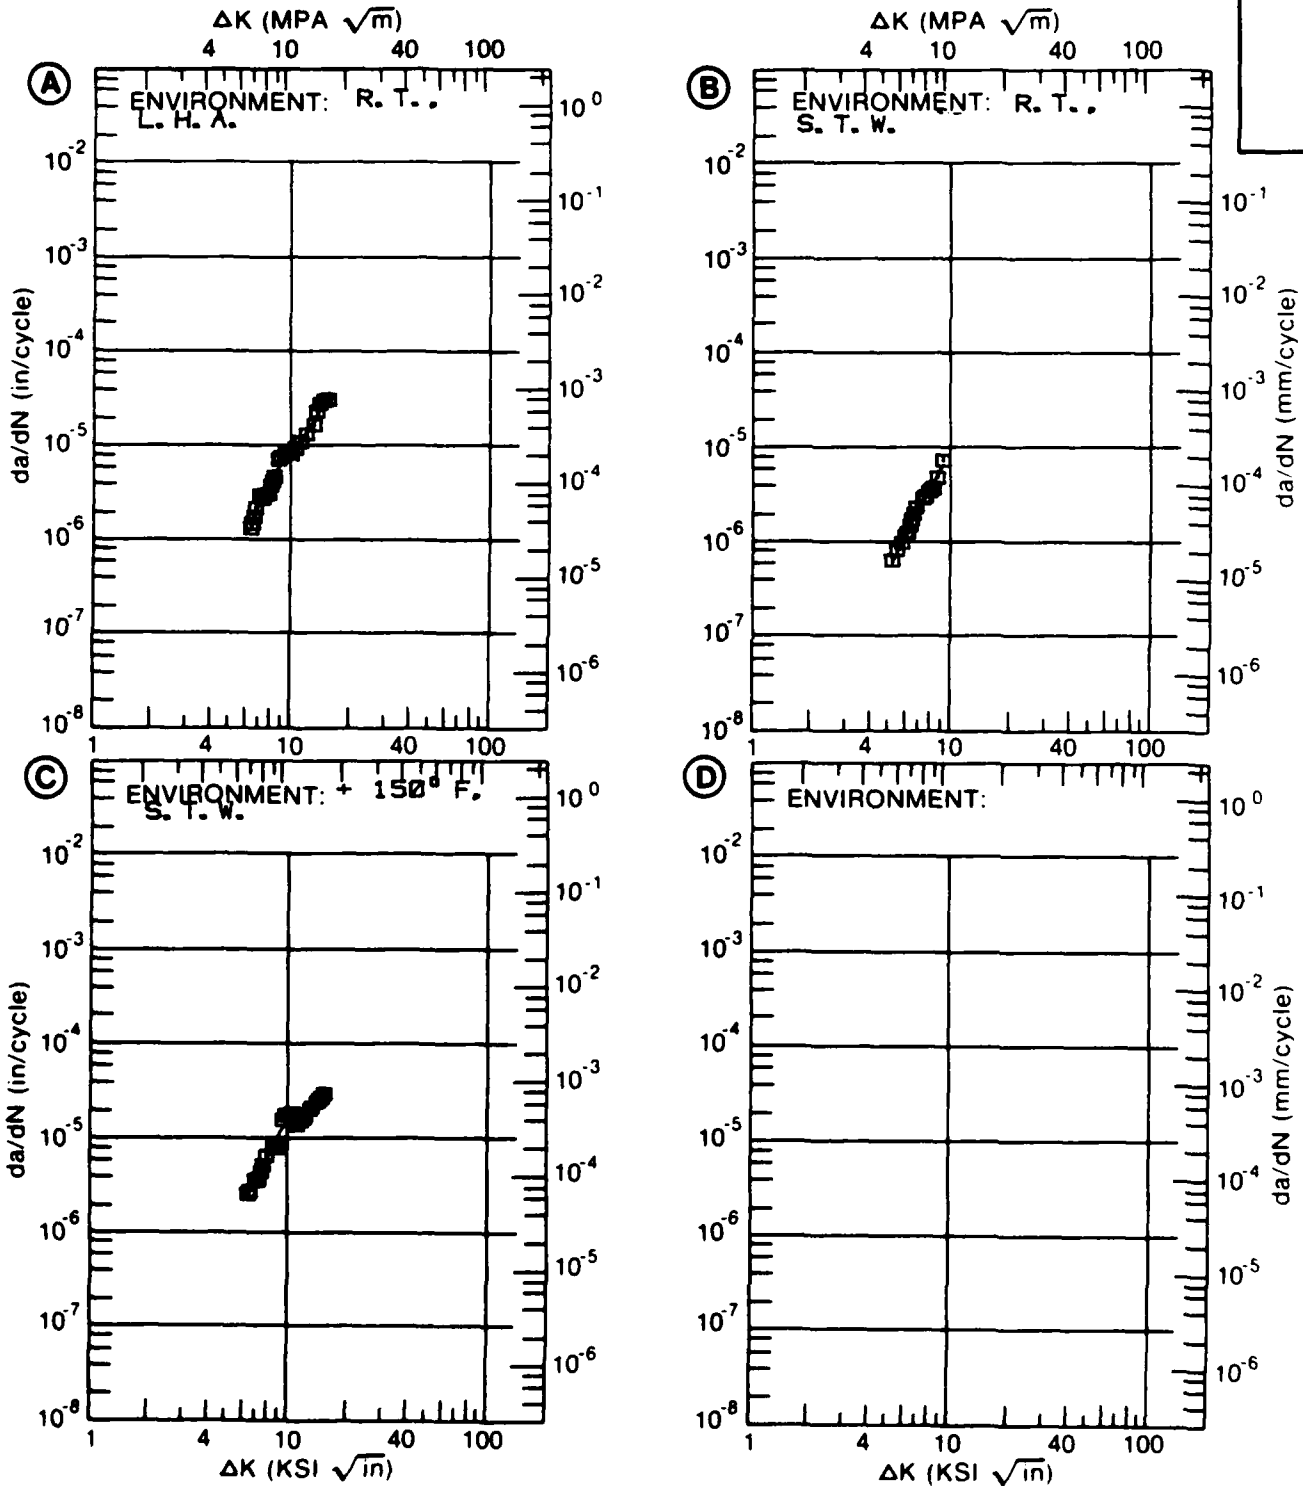


Figure 7.10.3.18

TABLE 7.10.3.19

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.19 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. F. C. S.	E= R. T. S. C. S.		
DELTA K MIN	A: 6.31	1.68			
	B: 6.13		1.62		
	C:				
	D:				
	7.00	2.43	2.48		
	8.00	3.76	3.77		
	9.00	5.37	5.41		
	10.00	7.26	7.42		
	13.00	14.8	15.9		
	16.00	26.1	28.4		
	20.00	50.0			
	25.00	104.			
	30.00	210.			
DELTA K MAX	A: 33.42	334.			
	B: 18.70		43.5		
	C:				
	D:				
ROOT MEAN SQUARE		12.94	4.49		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0		1	1	

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.990"
 SPECIMEN WIDTH: 6.010"
 REFERENCES: 88579

ALUM.
ALLOY

2219

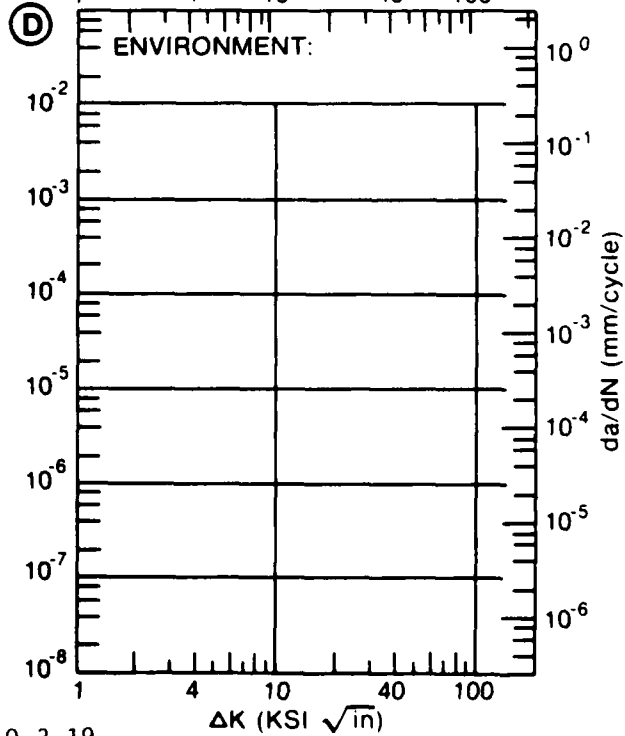
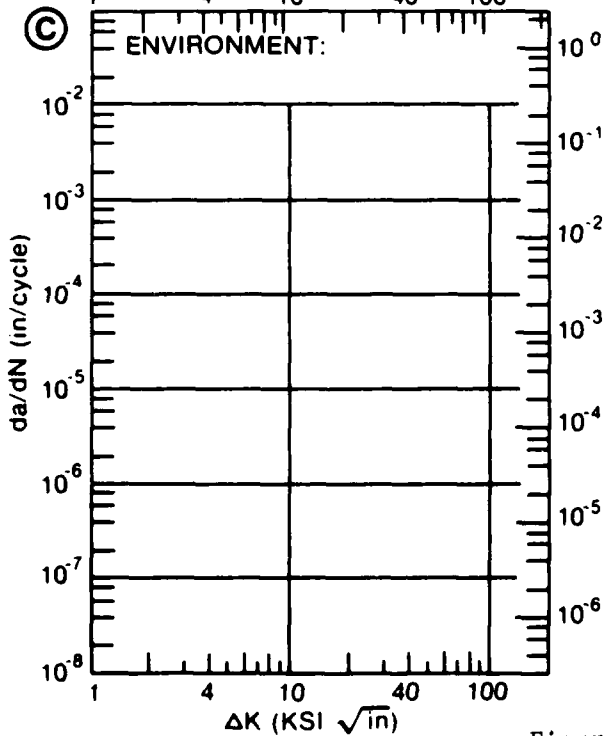
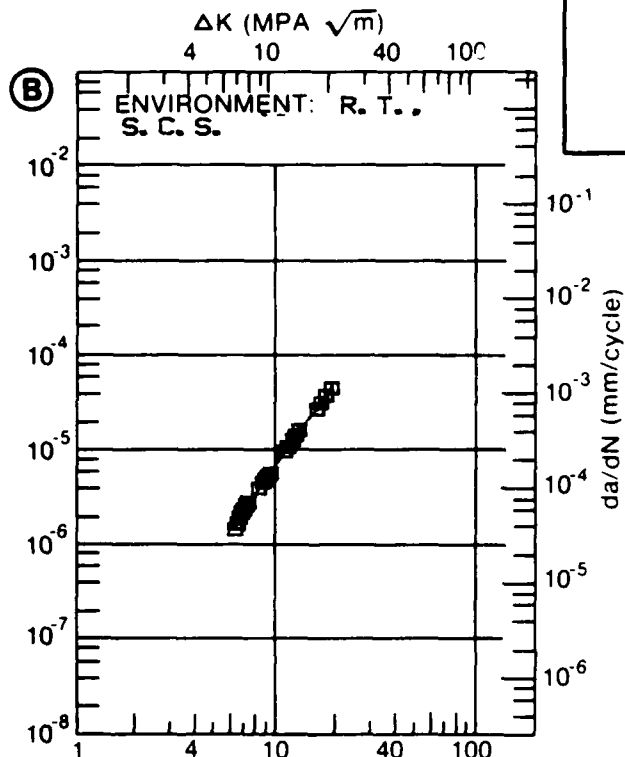
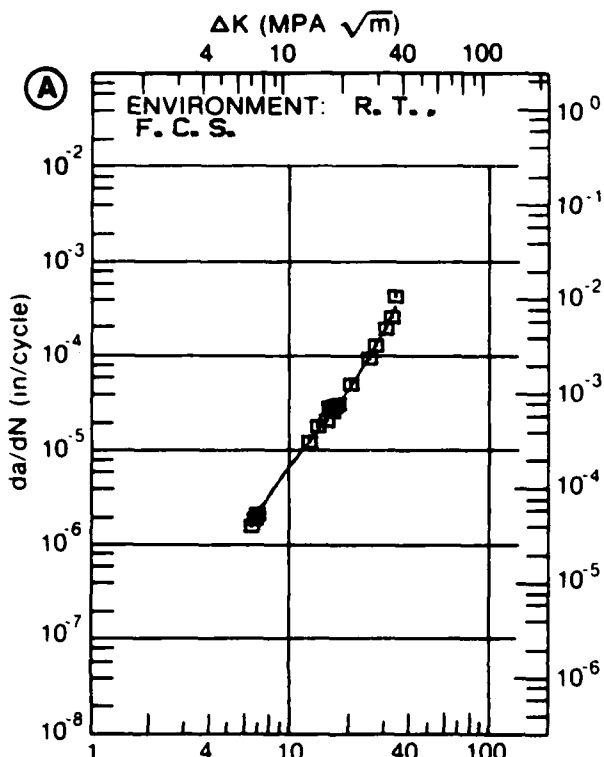


Figure 7.10.3.19

TABLE 7.10.3.20

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.20 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: TB51					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. S. T. W.		
DELTA K	A: 6.98	1.58			
MIN	B: 13.00		11.8		
	C:				
	D:				
	7.00	1.60			
	8.00	3.03			
	9.00	4.89			
	10.00	7.10			
	13.00	15.5	11.8		
	16.00	26.9	22.9		
	20.00		55.6		
	25.00		115.		
	30.00		245.		
DELTA K	A: 18.26	38.9			
MAX	B: 30.86		300.		
	C:				
	D:				
ROOT MEAN SQUARE		6.74	8.86		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 0.10 HZ

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.994- 1.000"
 SPECIMEN WIDTH: 6.000- 6.010"
 REFERENCES: 88579

ALUM.
ALLOY

2219

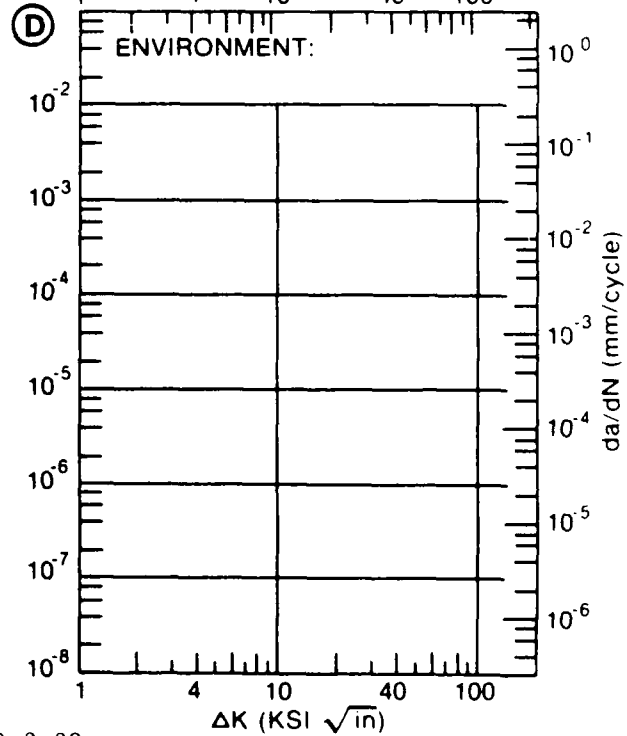
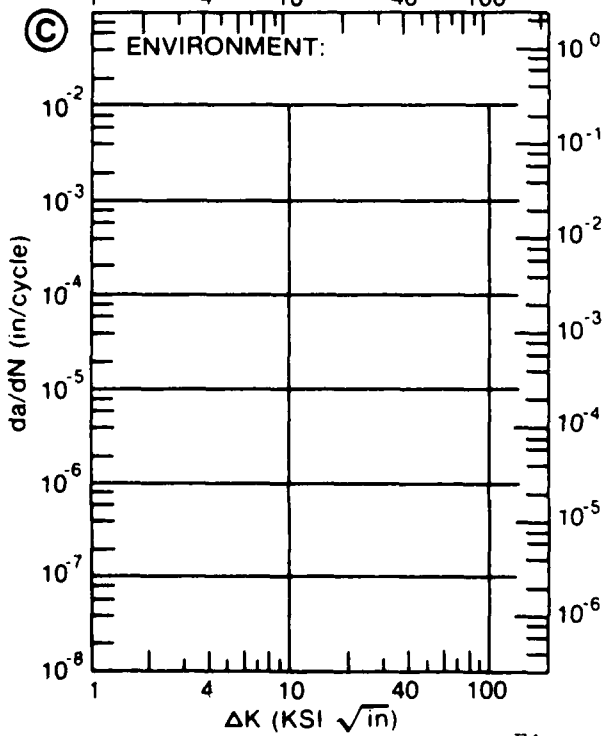
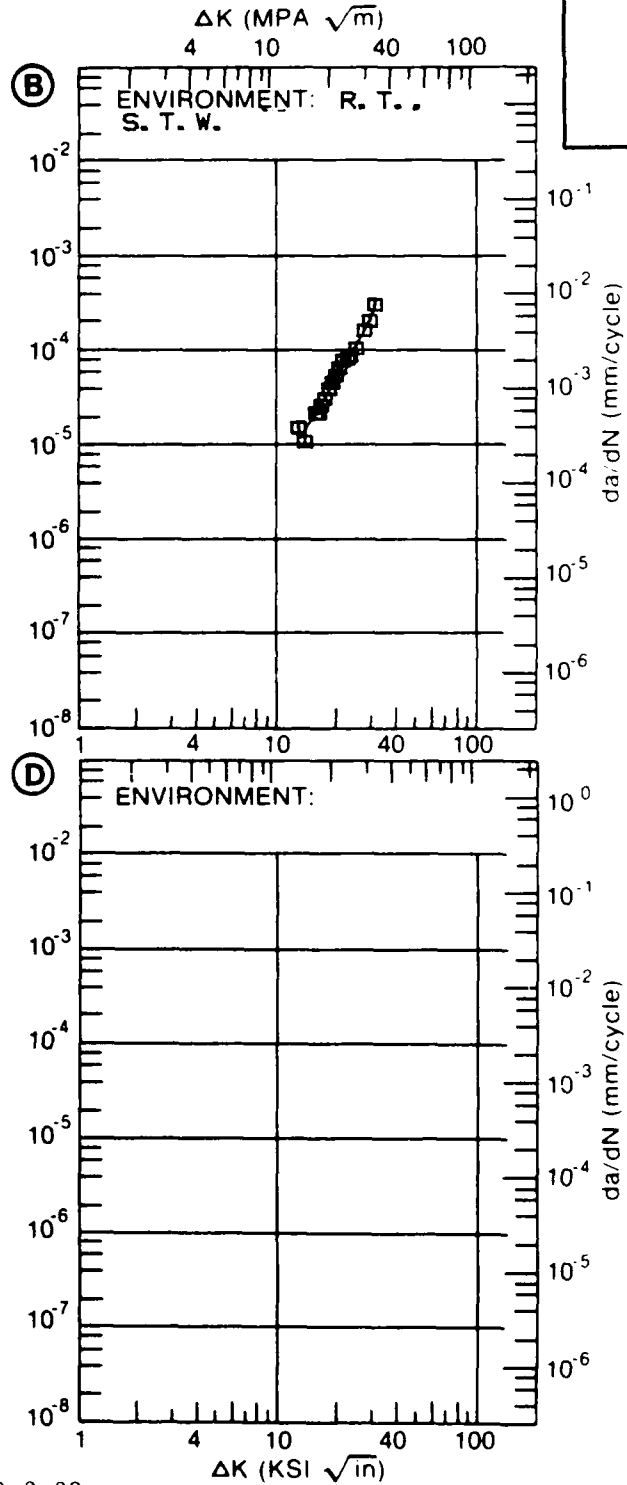
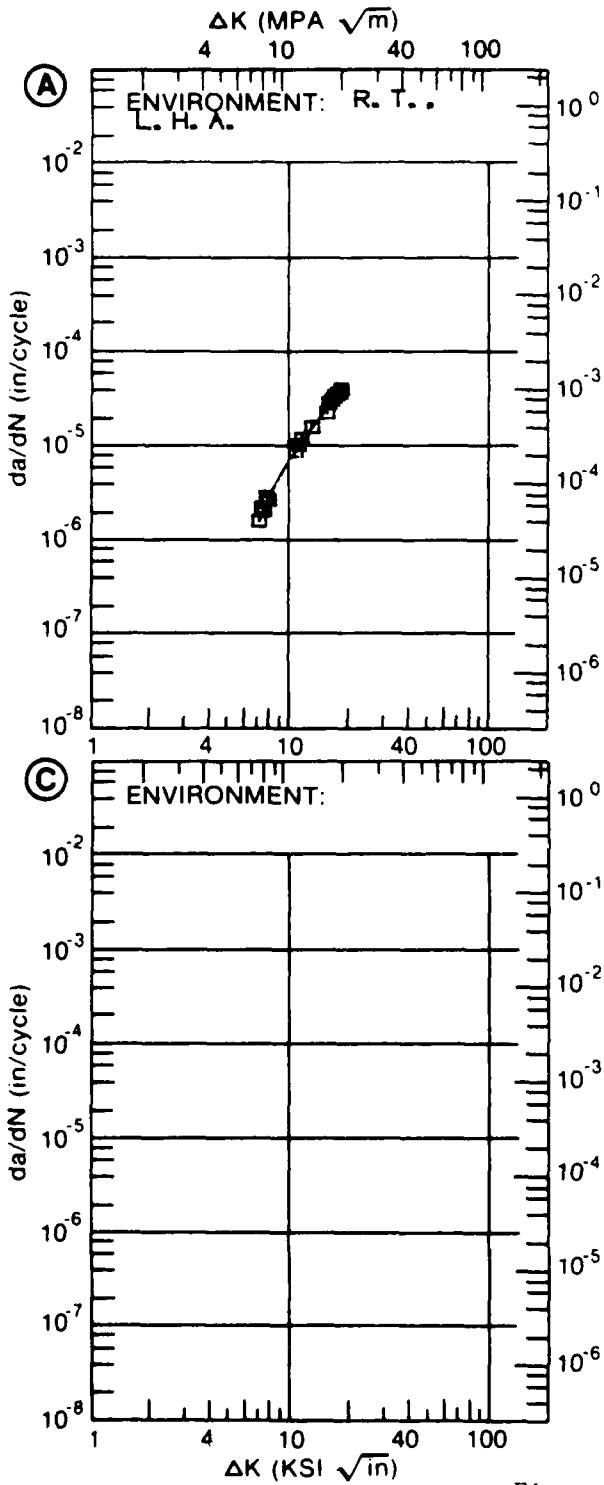


Figure 7.10.3.20

TABLE 7.10.3.21

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.21 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K	A: 3.09	.223			
MIN	B:				
	C:				
	D:				
	3.50	.256			
	4.00	.344			
	5.00	.723			
	6.00	1.49			
	7.00	2.76			
	8.00	4.49			
	9.00	6.41			
	10.00	8.15			
DELTA K	A: 10.70	9.05			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		13.61			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.50
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 49.6 KSI
 ULT. STRENGTH: 66.2 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837

ALUM. ALLOY
2219

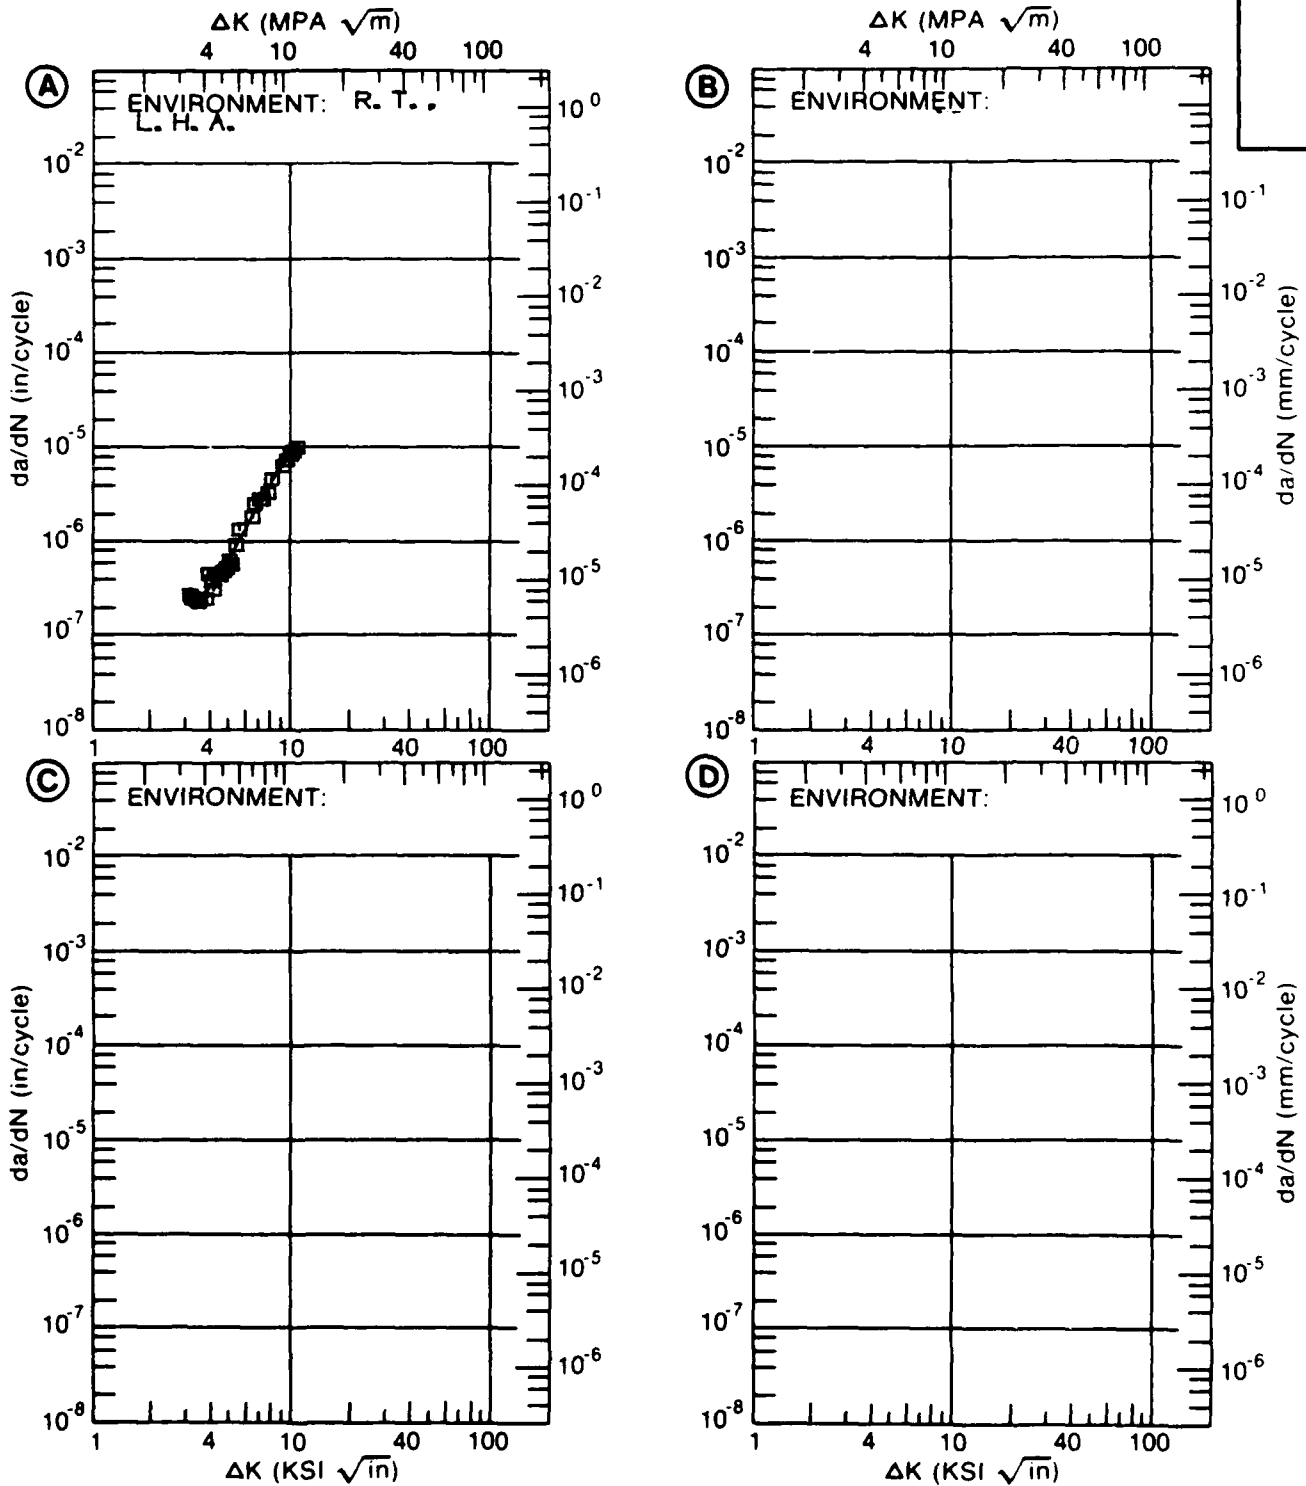


Figure 7.10-3.21
 7.10-69

TABLE 7.10.3.22

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.22 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM 2219
CONDITION: T851
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10**~6 IN. /CYCLE)			
		A	B	C	D
		F(HZ)= 63.30			
DELTA K MIN	A: 3.34	.0853			
	B:				
	C:				
	D:				
	3.50	.0823			
	4.00	.119			
	5.00	.282			
	6.00	.600			
	7.00	1.17			
	8.00	2.08			
9.00	3.30				
10.00	4.67				
DELTA K MAX	A: 11.59	6.57			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 19.22
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 49.6 KSI
 ULT. STRENGTH: 66.2 KSI
 SPECIMEN THK: 0.993"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

ALUM.
 ALLOY

2219

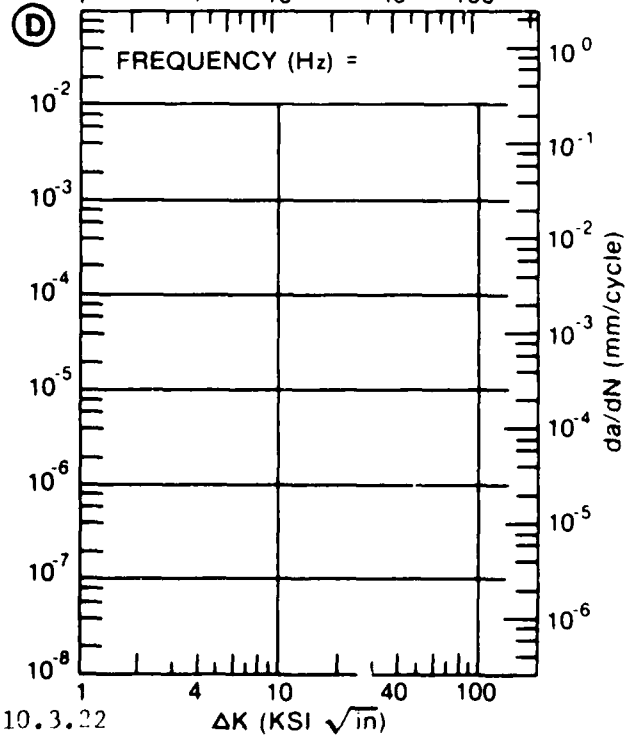
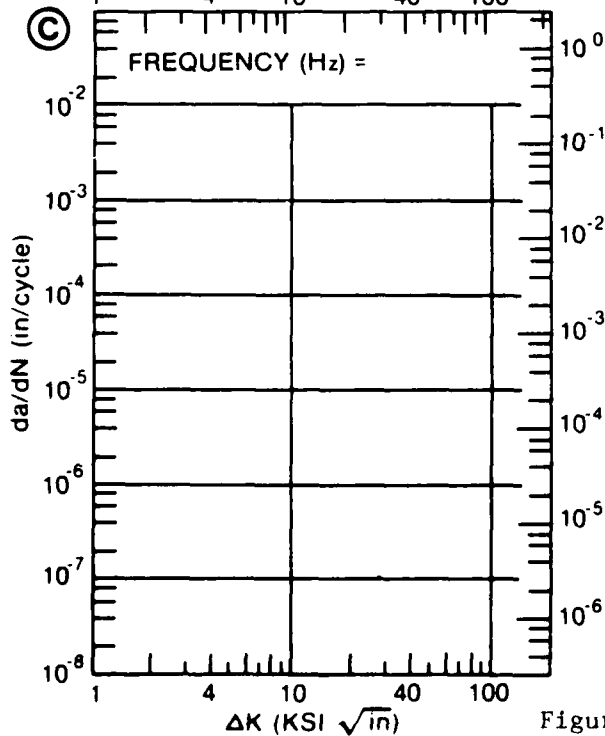
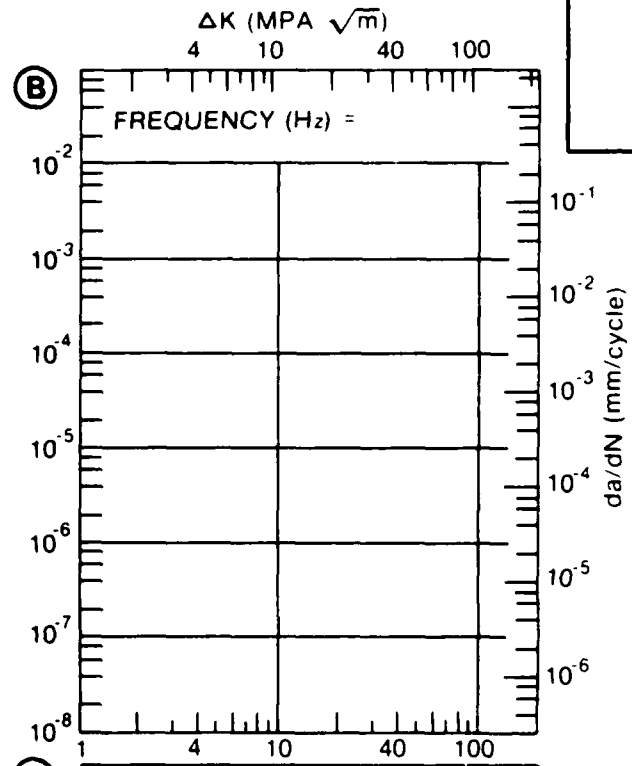
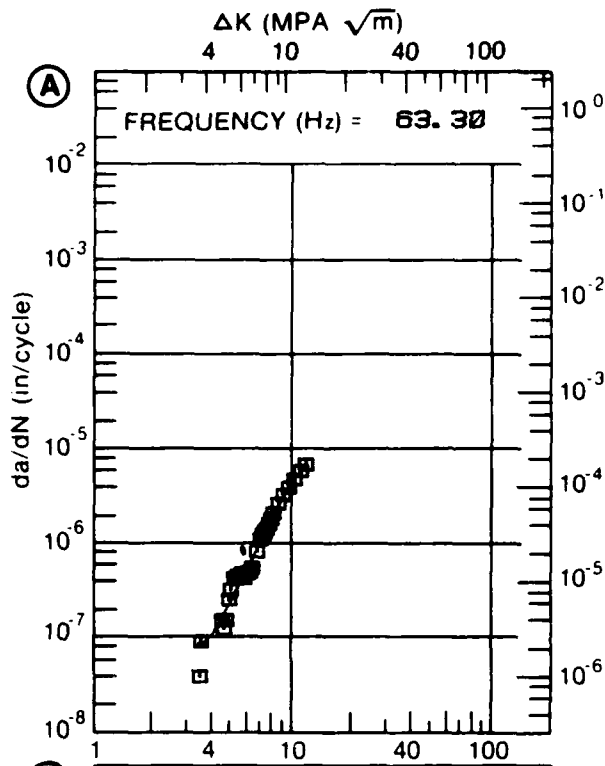


Figure 7.10.3.22

TABLE 7.10.3.23

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.23 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A., 6HZ	E=+ 265F L. H. A., 6HZ	E= R. T. S. T. W., 1HZ	
DELTA K	A: 7.12	1.40			
MIN	B: 6.69		1.96		
	C: 4.01			.246	
	D:				
	5.00			1.02	
	6.00			2.42	
	7.00		2.36	4.24	
	8.00	2.52	3.90	6.28	
	9.00	3.97	5.88	8.46	
	10.00	5.43	8.32	10.8	
	13.00	9.66	19.2	19.8	
	16.00	15.4	38.2	35.2	
	20.00	33.3	88.6	81.5	
	25.00	121.	244.	268.	
	30.00	616.			
DELTA K	A: 32.50	1536.			
MAX	B: 25.72		282.		
	C: 29.24			815.	
	D:				
ROOT MEAN SQUARE		11.01	9.22	23.95	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 1.75" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 48.0 KSI
 ULT. STRENGTH: 85.9- 86.0 KSI
 SPECIMEN THK: 0.995- 1.000"
 SPECIMEN WIDTH: 6.000- 6.010"
 REFERENCES: 88579, 85837

ALUM.
ALLOY

2219

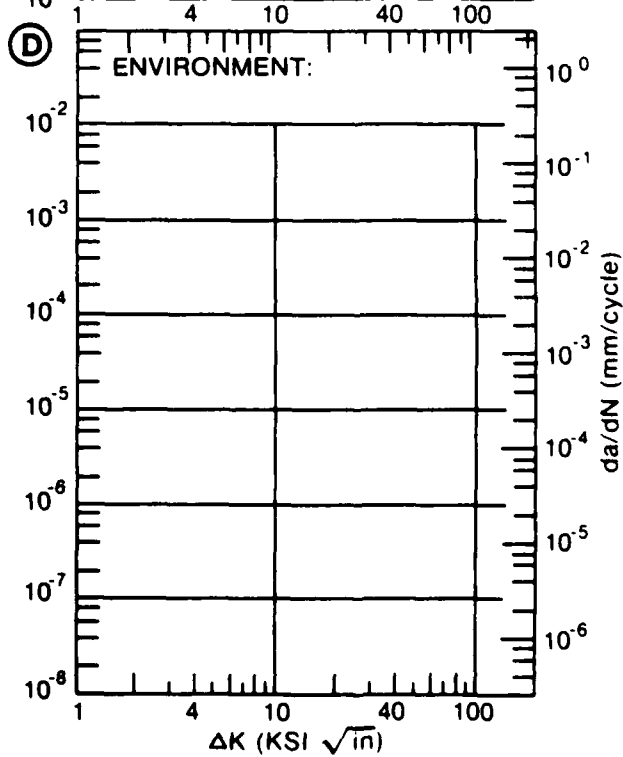
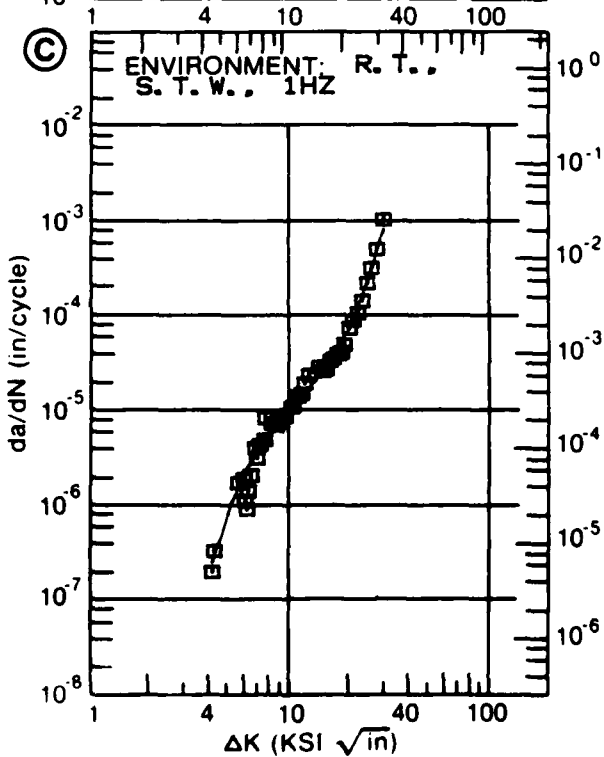
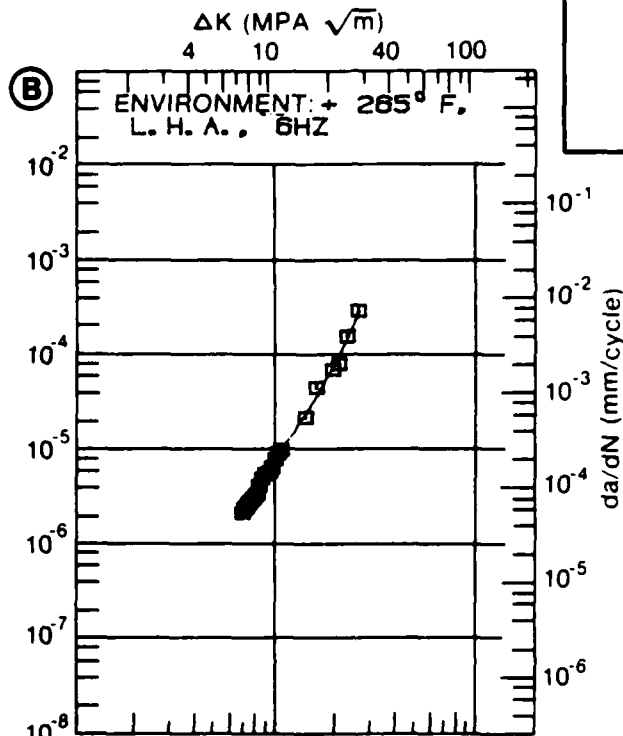
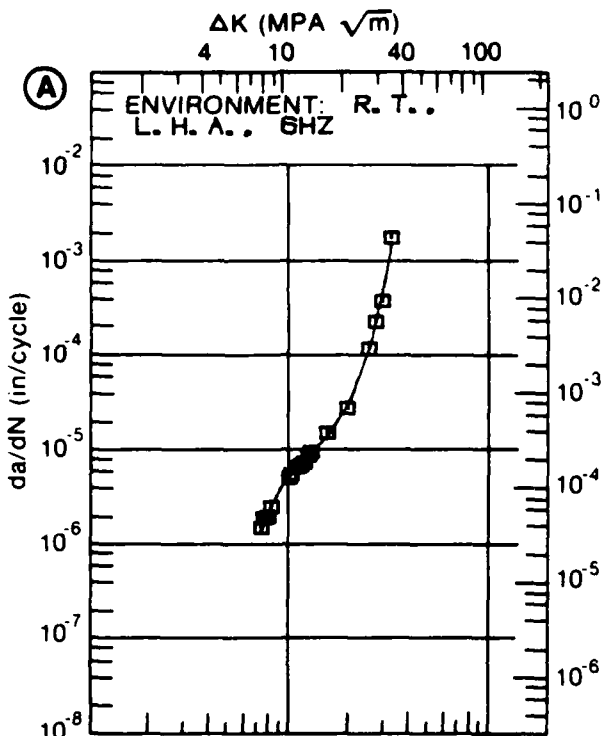


Figure 7.10.3.23

TABLE 7.10.3.24

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.24 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219	
CONDITION: T851			
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)	
		A	B
		E= R. T. L. H. A.	E= R. T. S. T. W.
		C	D
DELTA K	A: 5.95	1.30	
MIN	B: 6.48		1.21
	C:		
	D:		
	6.00	1.35	
	7.00	2.51	2.02
	8.00	3.98	4.25
	9.00	5.72	7.20
	10.00	7.74	10.6
	13.00	15.8	22.1
	16.00	28.5	35.1
	20.00	60.3	59.5
	25.00	155.	119.
	30.00	411.	
DELTA K	A: 32.68	700.	
MAX	B: 27.75		183.
	C:		
	D:		
ROOT MEAN SQUARE		32.94	13.81
PERCENT ERROR			
LIFE	0.0-0.5		
PREDICTION	0.5-0.8	1	
RATIO	0.8-1.25	1	1
SUMMARY	1.25-2.0		
(NP/NA)	>2.0		

CONDITION/HT: T851
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 49.6- 50.0 KSI
 ULT. STRENGTH: 86.2- 88.0 KSI
 SPECIMEN THK: 0.993- 1.000"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 88579, 85837

ALUM.
ALLOY

2219

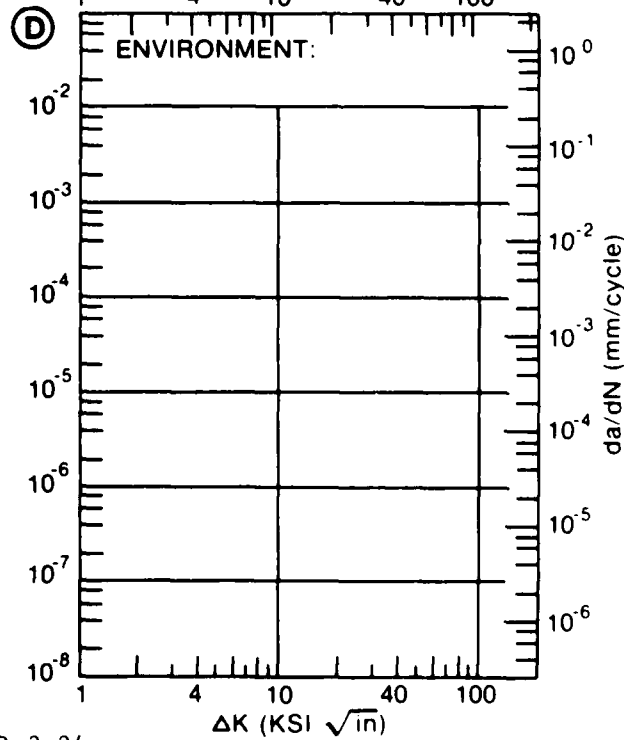
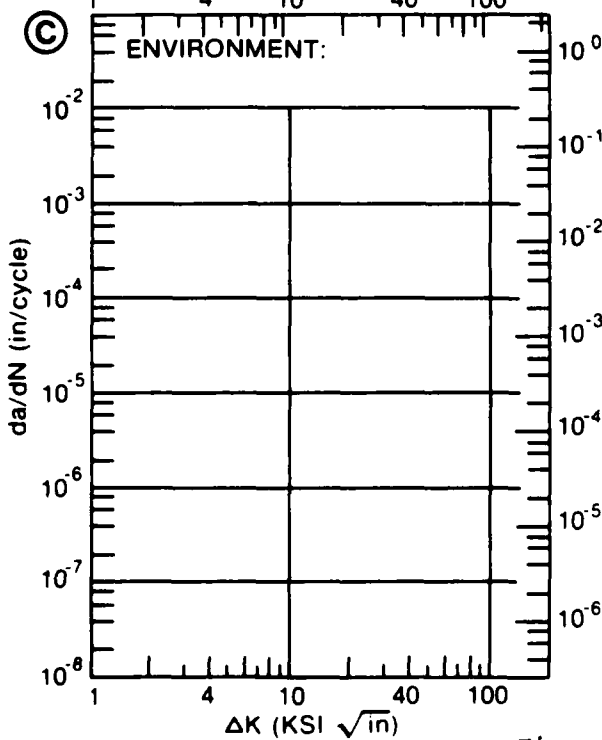
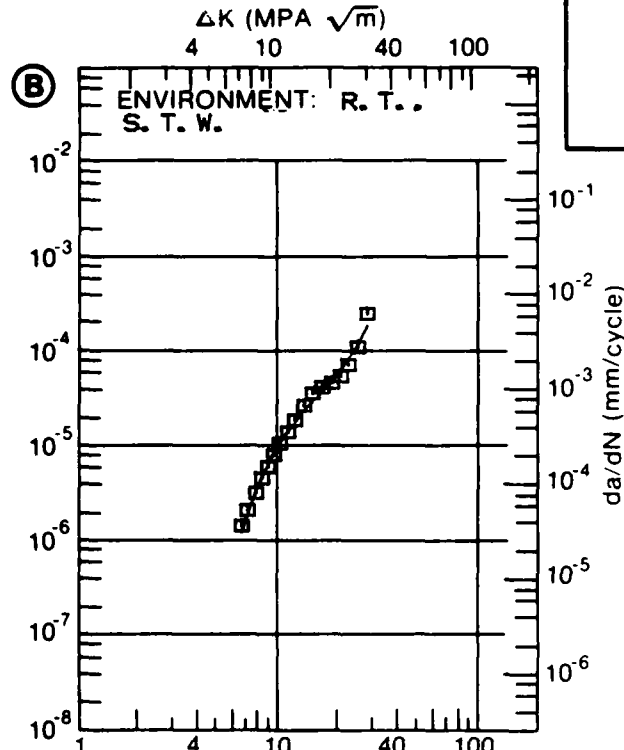
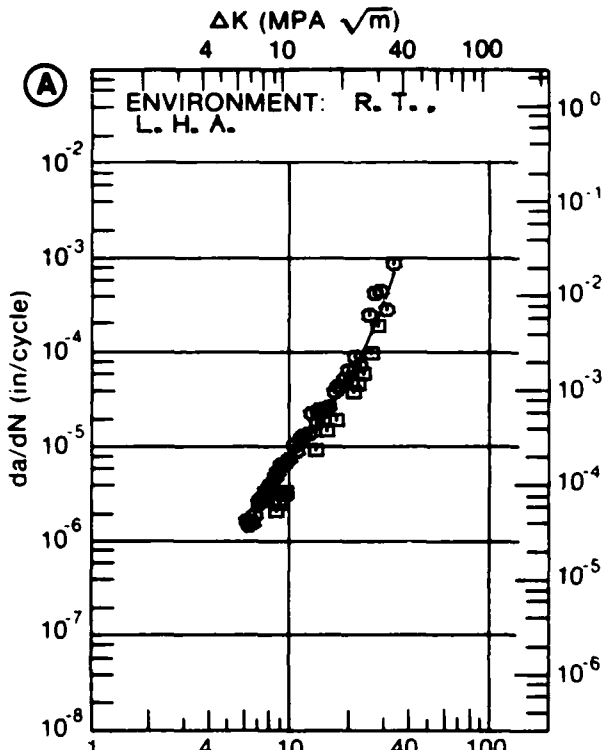


Figure 7.10.3.24

TABLE 7.10.3.25

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219	
CONDITION: T851			
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)	
		A	B
		E= R. T. L. H. A.	E= R. T. DIST. H2O
		C	D
DELTA K	A: 5.66	.982	
MIN	B: 6.07		1.39
	C:		
	D:		
	6.00	1.19	
	7.00	2.03	2.51
	8.00	3.35	4.06
	9.00	5.18	5.93
	10.00	7.60	8.09
	13.00	18.0	16.4
	16.00	30.8	28.6
	20.00	54.0	55.7
	25.00	125.	124.
	30.00	347.	304.
	35.00	1218.	1118.
DELTA K	A: 35.37	1401.	
MAX	B: 36.90		2114.
	C:		
	D:		
ROOT MEAN SQUARE		16.22	10.10
PERCENT ERROR			
LIFE	0.0-0.5		
PREDICTION	0.5-0.8		
RATIO	0.8-1.25	1	2
SUMMARY	1.25-2.0		
(NP/NA)	>2.0		

CONDITION/HT: T851
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY: 1.00 HZ

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 68.0 KSI
 SPECIMEN THK: 0.990"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 88579

ALUM. ALLOY
2219

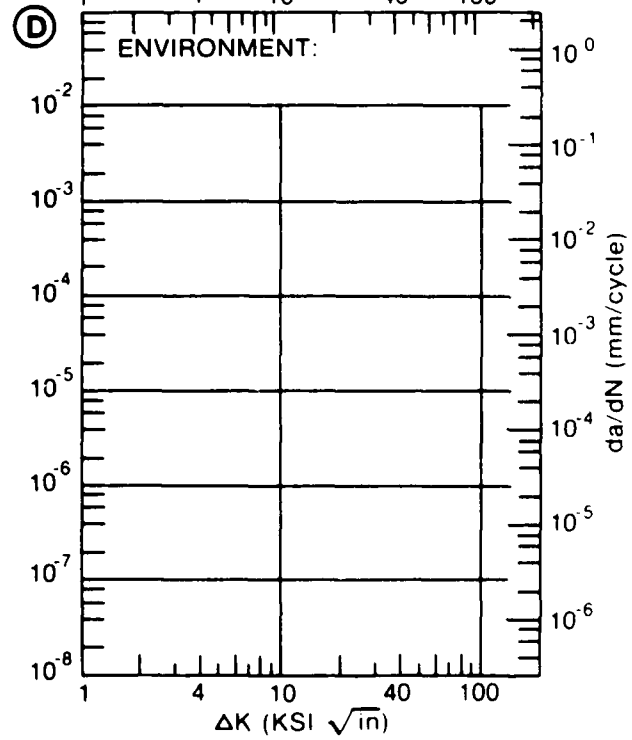
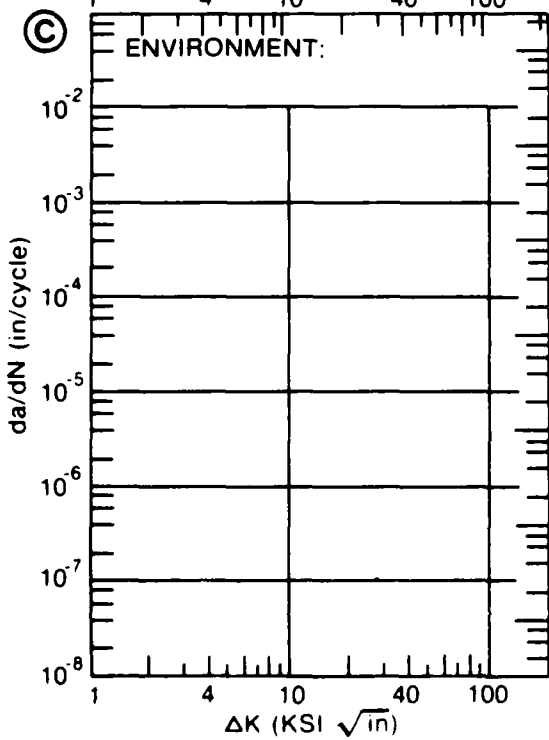
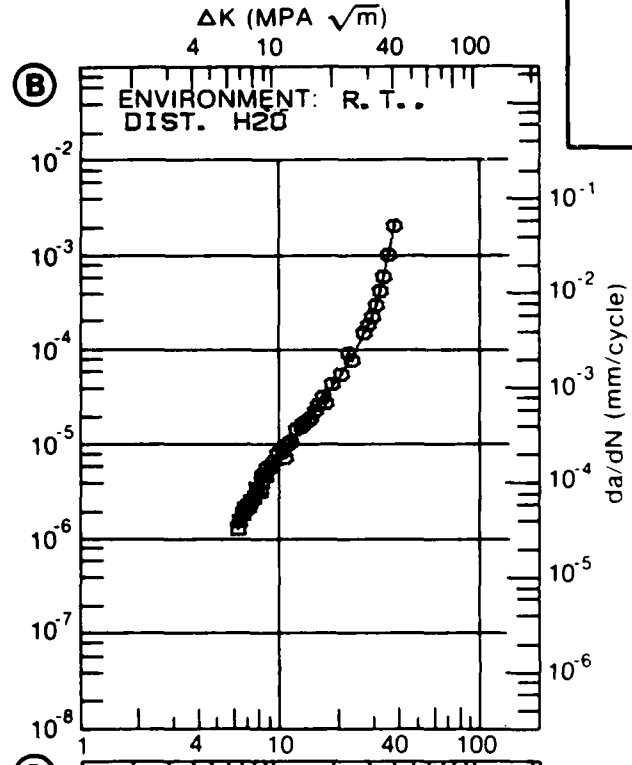
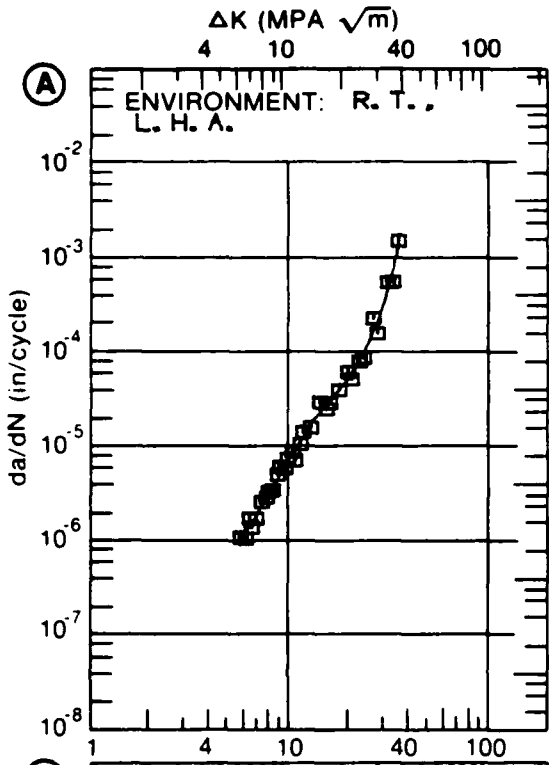


Figure 7.10.3.25

TABLE 7.10.3.26

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.26 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.			
DELTA K A:	5.67	1.43			
DELTA K B:					
MIN C:					
D:					
	6.00	1.76			
	7.00	2.97			
	8.00	4.50			
	9.00	6.39			
	10.00	8.71			
	13.00	19.3			
	16.00	39.6			
	20.00	100.			
	25.00	317.			
DELTA K A:	29.91	989.			
DELTA K B:					
MAX C:					
D:					
ROOT MEAN SQUARE		32.37			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY: 6.00 HZ

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 88.0 KSI
 SPECIMEN THK: 0.990"
 SPECIMEN WIDTH: 5.990"
 REFERENCES: 88579

ALUM.
 ALLOY
 2219

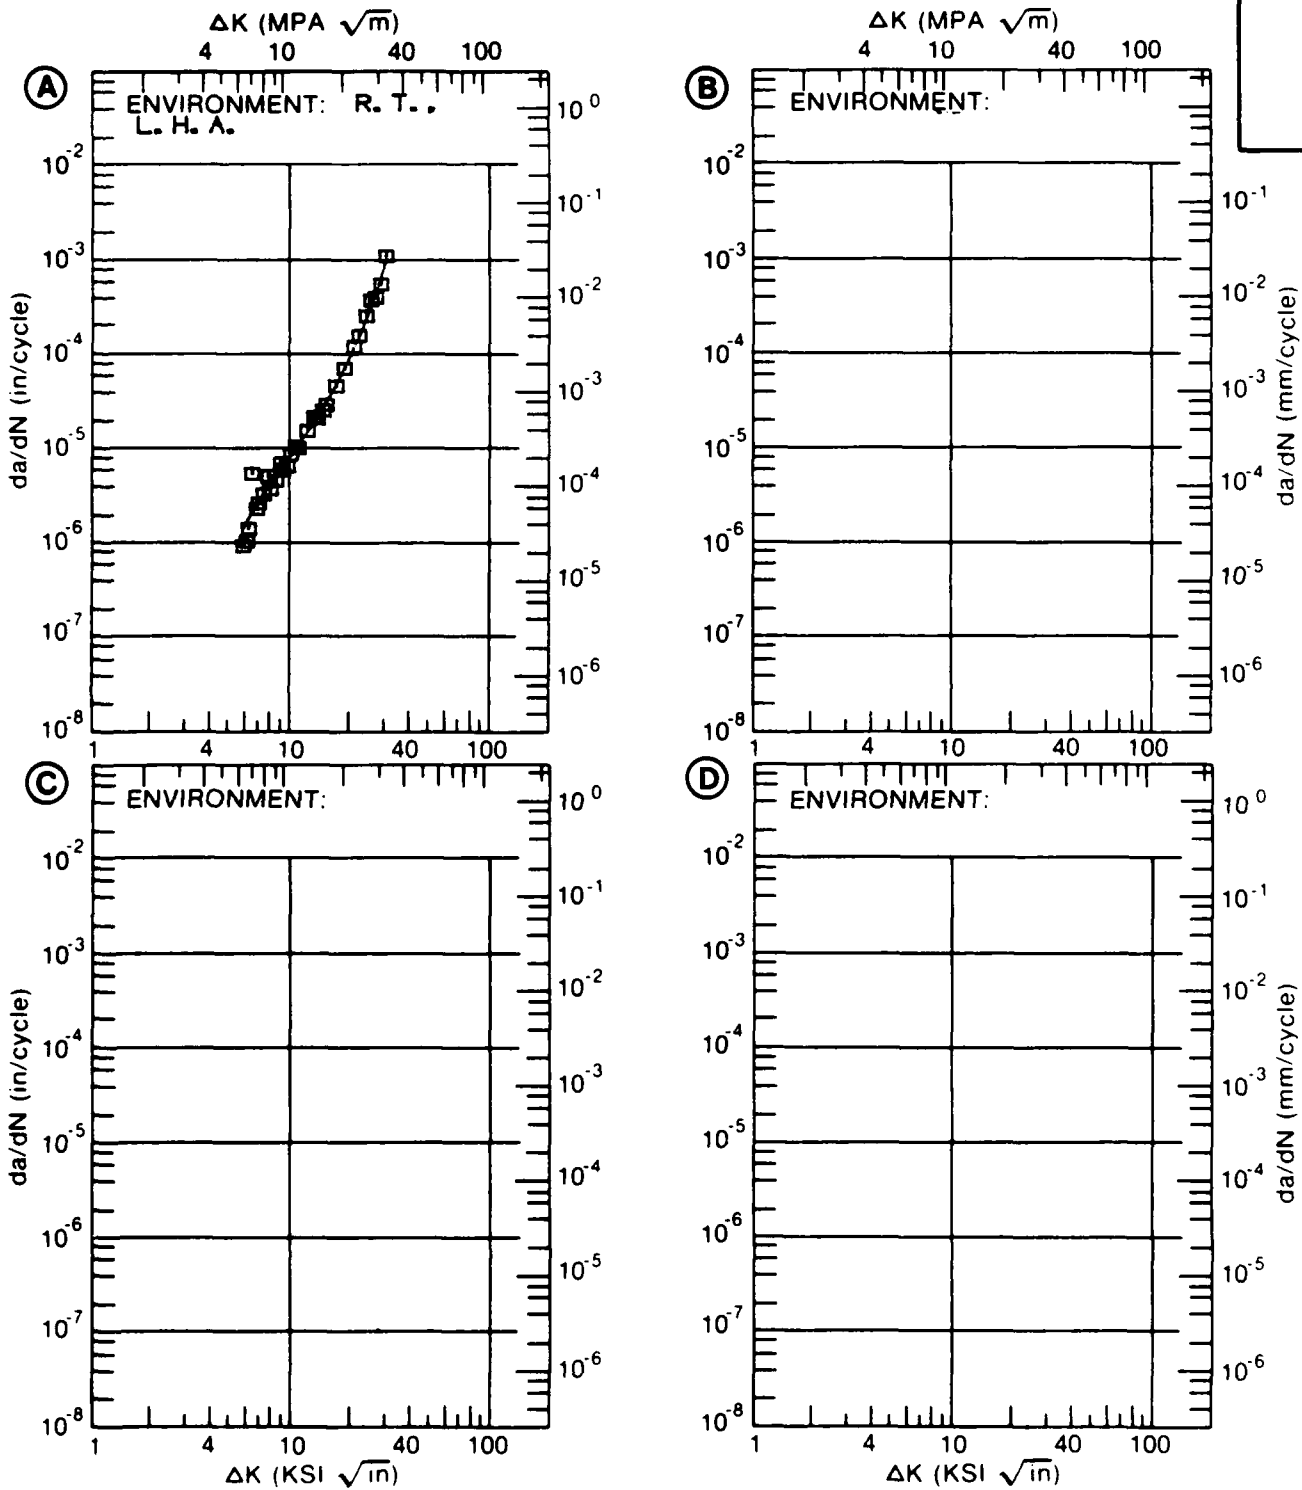


Figure 7.10.3.26

TABLE 7.10.3.27

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.27 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A. 6HZ	E= R. T. S. T. W. 1HZ		
DELTA K	A: 6.28	1.31			
MIN	B: 8.43		3.46		
	C:				
	D:				
	7.00	1.65			
	8.00	2.25			
	9.00	3.01	4.60		
	10.00	3.95	7.14		
	13.00	7.96	17.6		
	16.00	13.8	30.1		
	20.00	24.4	64.0		
	25.00	67.4	206.		
DELTA K	A: 28.98	267.			
MAX	B: 28.46		386.		
	C:				
	D:				
ROOT MEAN SQUARE		32.80	14.62		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 53.0- 54.0 KSI
 ULT. STRENGTH: 67.0- 69.0 KSI
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579

ALUM.
ALLOY

2219

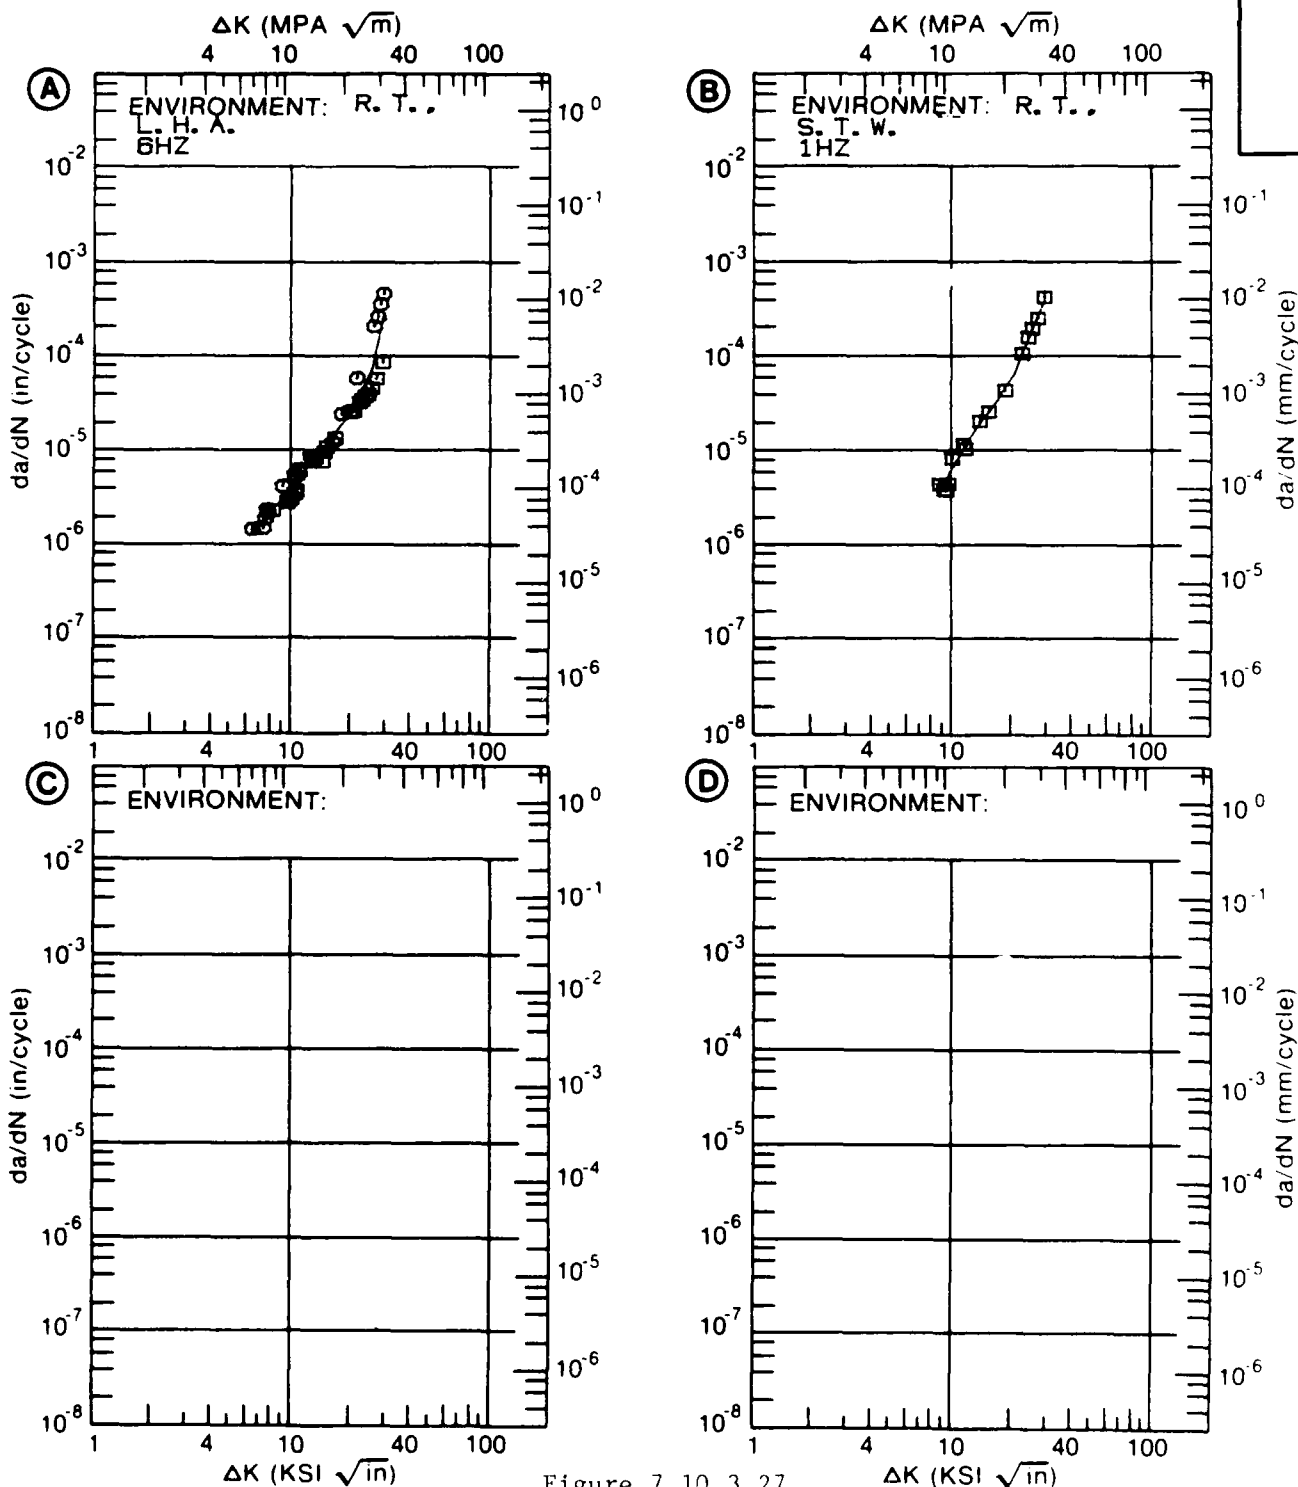


Figure 7.10.3.27

TABLE 7.10.3.28

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.28 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		2219				
CONDITION: T851						
ENVIRONMENT: R. T. , S. T. W.						
DELTA K (KSI*IN**1/2)			DA/DN (10**-6 IN. /CYCLE)			
			A	B	C	D
			R=+0.08			
DELTA K MIN	A:	10.27	13.7			
	B:					
	C:					
	D:					
		13.00	22.3			
DELTA K MAX	A:	15.94	45.7			
	B:					
	C:					
	D:					
ROOT MEAN SQUARE		8.57				
PERCENT ERROR						
LIFE	0.0-0.5					
PREDICTION	0.5-0.8					
RATIO	0.8-1.25	1				
SUMMARY	1.25-2.0					
(NP/NA)	>2.0					

CONDITION/HT: T851
 FORM: 3.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T., S. T. W.

YIELD STRENGTH: 53.0 KSI
 ULT. STRENGTH: 68.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579

ALUM. ALLOY
2219




Figure 7.10.3.28

TABLE 7.10.3.29

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.29 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219
CONDITION: T8511
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)	DA/DN (10**--6 IN. /CYCLE)			
	A	B	C	D
	R=+0.08	R=+0.30		
A: 4.70	.155			
DELTA K B: 5.64		.629		
MIN C:				
D:				
5.00	.234			
6.00	.415	.747		
7.00	.622	1.30		
8.00	.908	2.32		
9.00	1.36	3.99		
10.00	2.12	6.44		
13.00	9.11	17.6		
16.00	22.1	26.5		
A: 18.71	23.1			
DELTA K B: 17.17		27.2		
MAX C:				
D:				

ROOT MEAN SQUARE 15.28 9.31
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T8511
 FORM: 1.75" TH EXTRUDED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 51.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.992- 0.993"
 SPECIMEN WIDTH: 6.000"
 REFERENCES 85837

ALUM.
ALLOY

2219

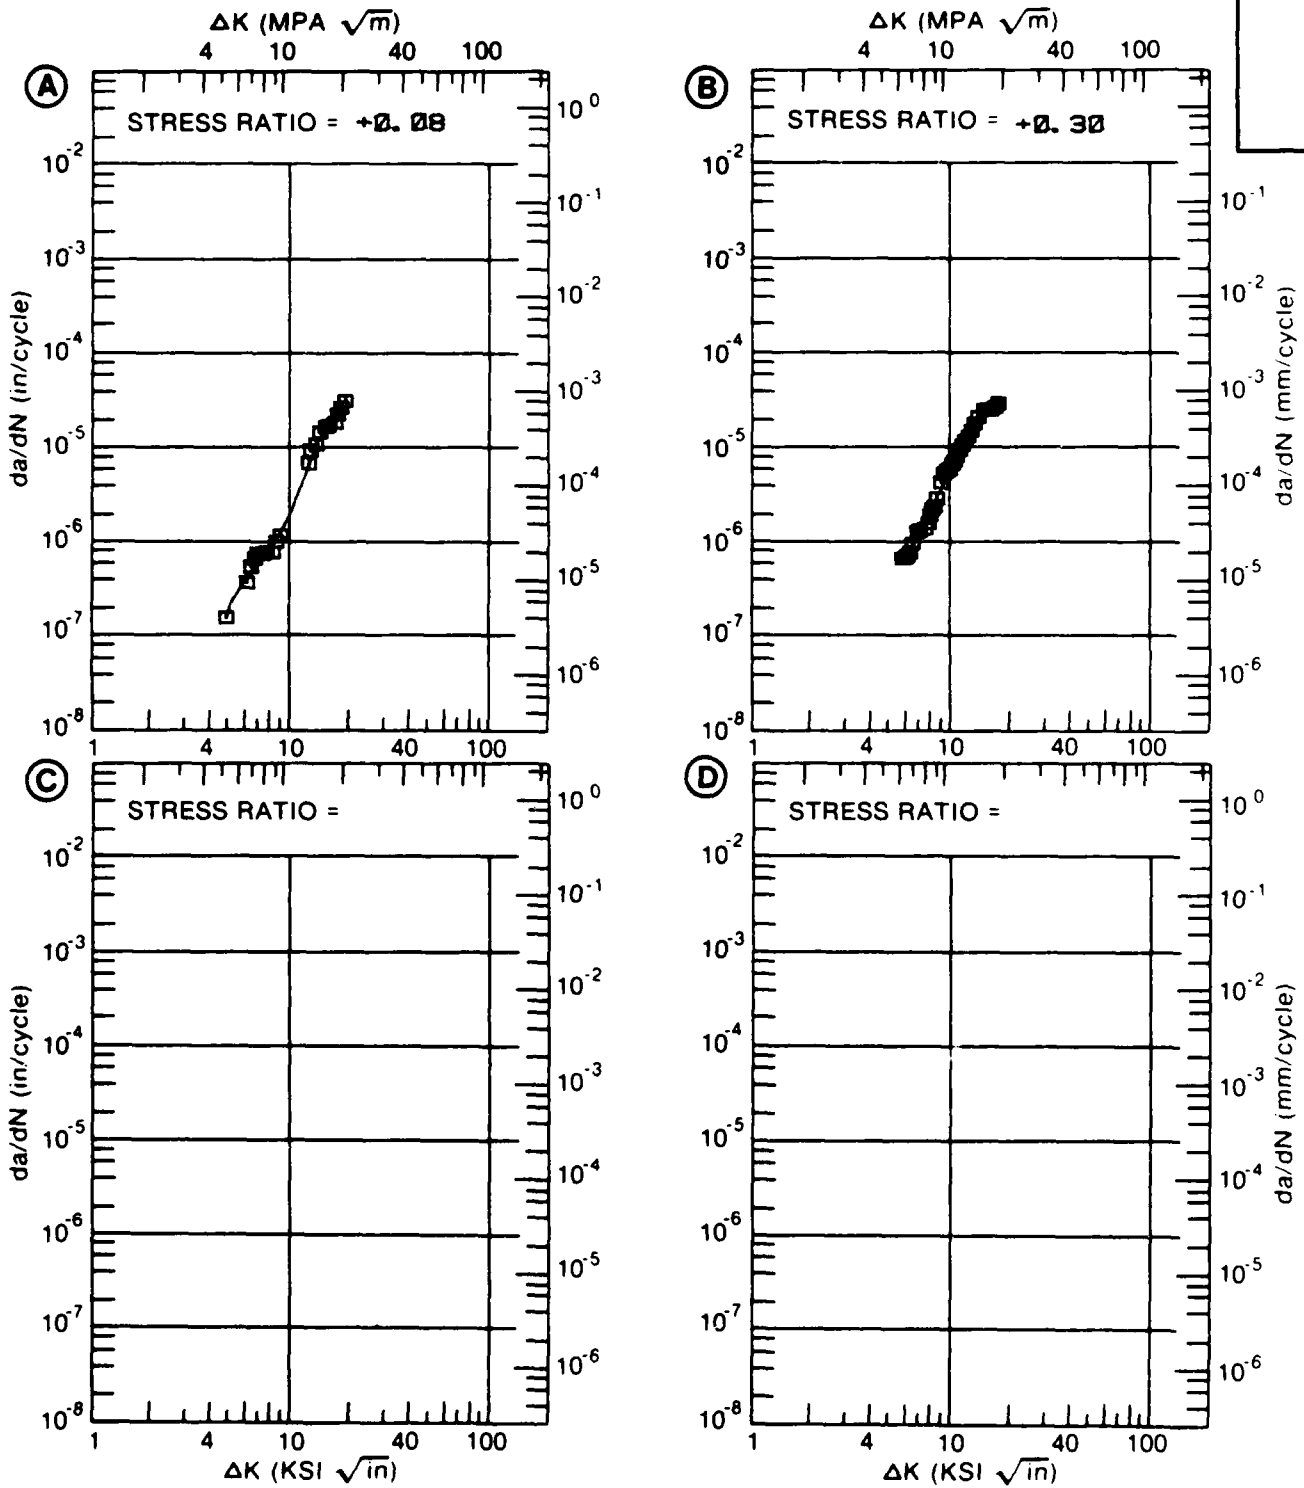


Figure 7.10.3.29

TABLE 7.10.3.30

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.30 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219
CONDITION: T8511
ENVIRONMENT: R. T. , S. T. W.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 7.84	2.76			
	B:				
	C:				
	D:				
	8.00	2.98			
	9.00	4.78			
	10.00	7.39			
	13.00	19.8			
DELTA K MAX	A: 14.17	25.4			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 12.05
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T8511
 FORM: 1.75" TH EXTRUDED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 1.00 HZ
 ENVIRONMENT: R. T. . S. T. W.

YIELD STRENGTH: 51.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.992"
 SPECIMEN WIDTH: 6.000"
 REFERENCES 85837

ALUM. ALLOY
2219

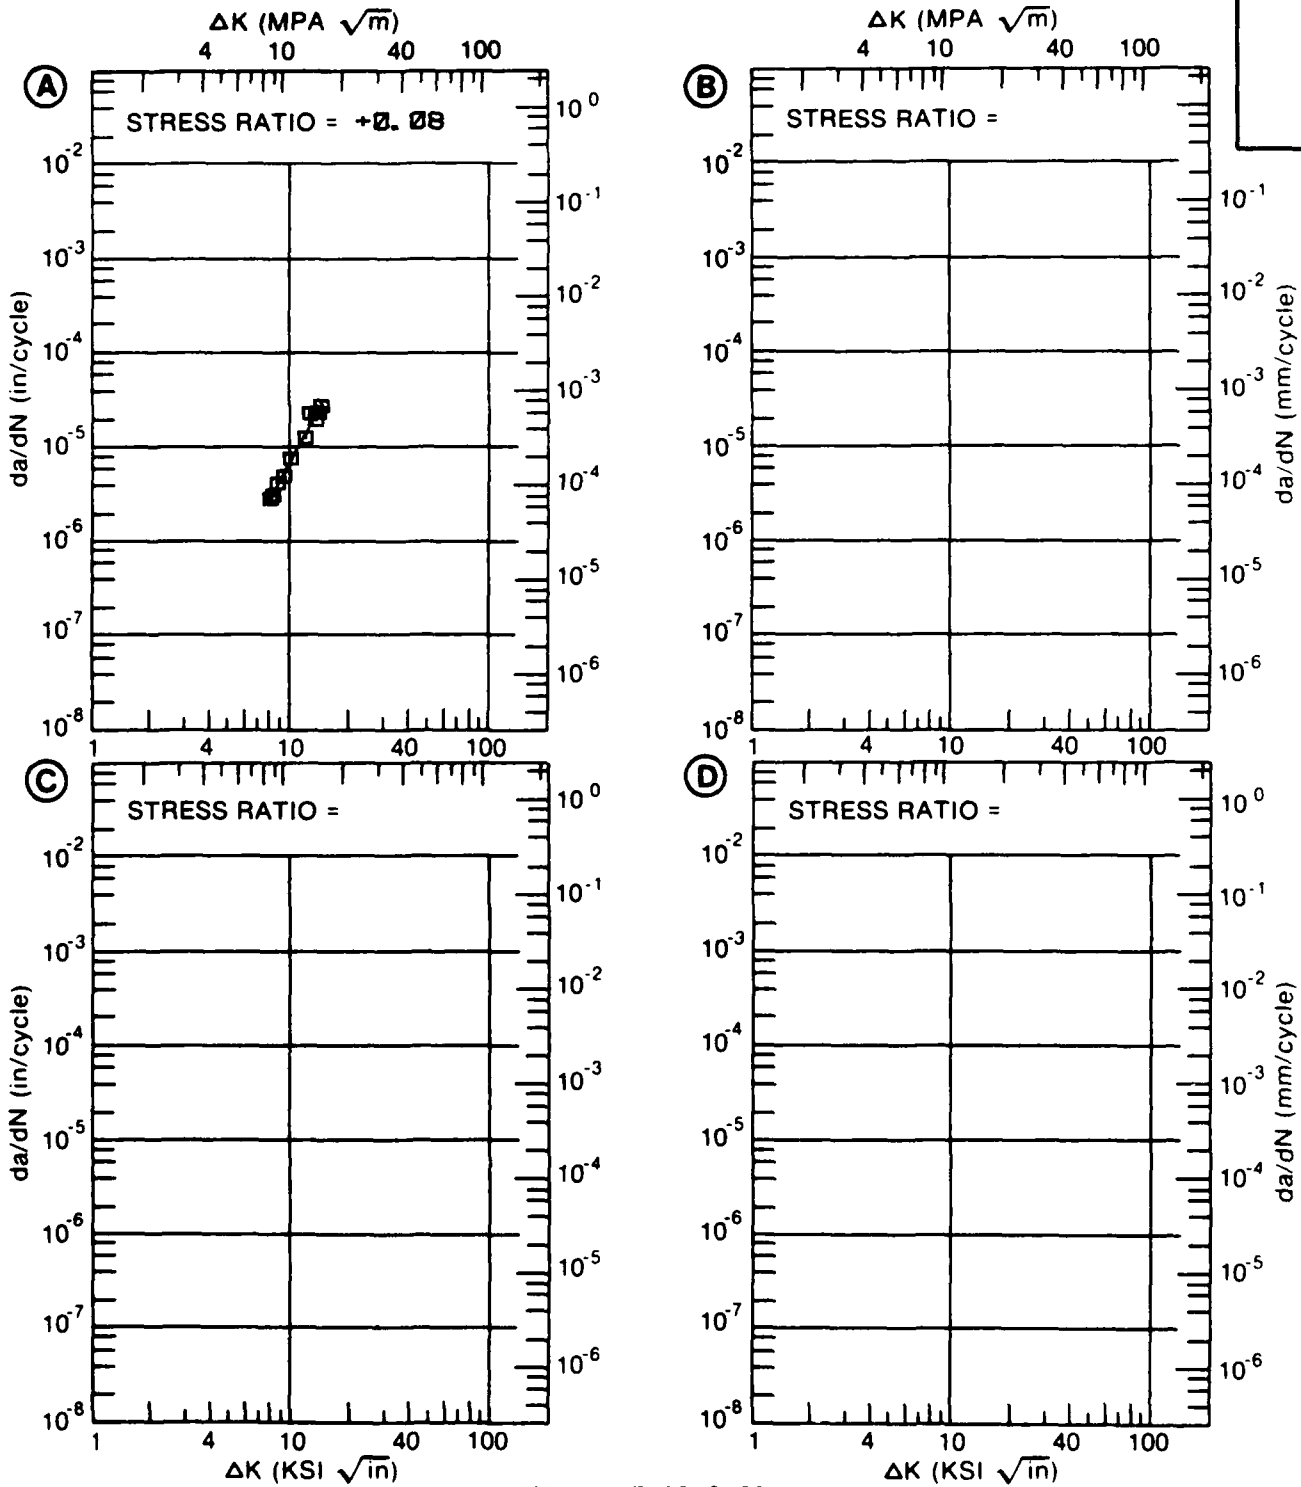


Figure 7.10.3.30

TABLE 7.10.3.31

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T8511					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.			
		L. H. A.		S. T. W.	
		6HZ		1HZ	
A:	5.85	.685			
DELTA K B:	4.86		.562		
MIN C:					
D:					
	5.00		.645		
	6.00	.763	1.42		
	7.00	1.37	2.47		
	8.00	2.14	3.79		
	9.00	3.08	5.40		
	10.00	4.26	7.37		
	13.00	10.5	16.7		
	16.00	26.5			
A:	16.35	29.6			
DELTA K B:	15.36		30.6		
MAX C:					
D:					
ROOT MEAN SQUARE		7.85	7.26		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T8511
 FORM: 1.75" TH EXTRUDED BAR
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 51.0 KSI
 ULT. STRENGTH: 66.0 KSI
 SPECIMEN THK: 0.990- 0.995"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837

ALUM. ALLOY
2219

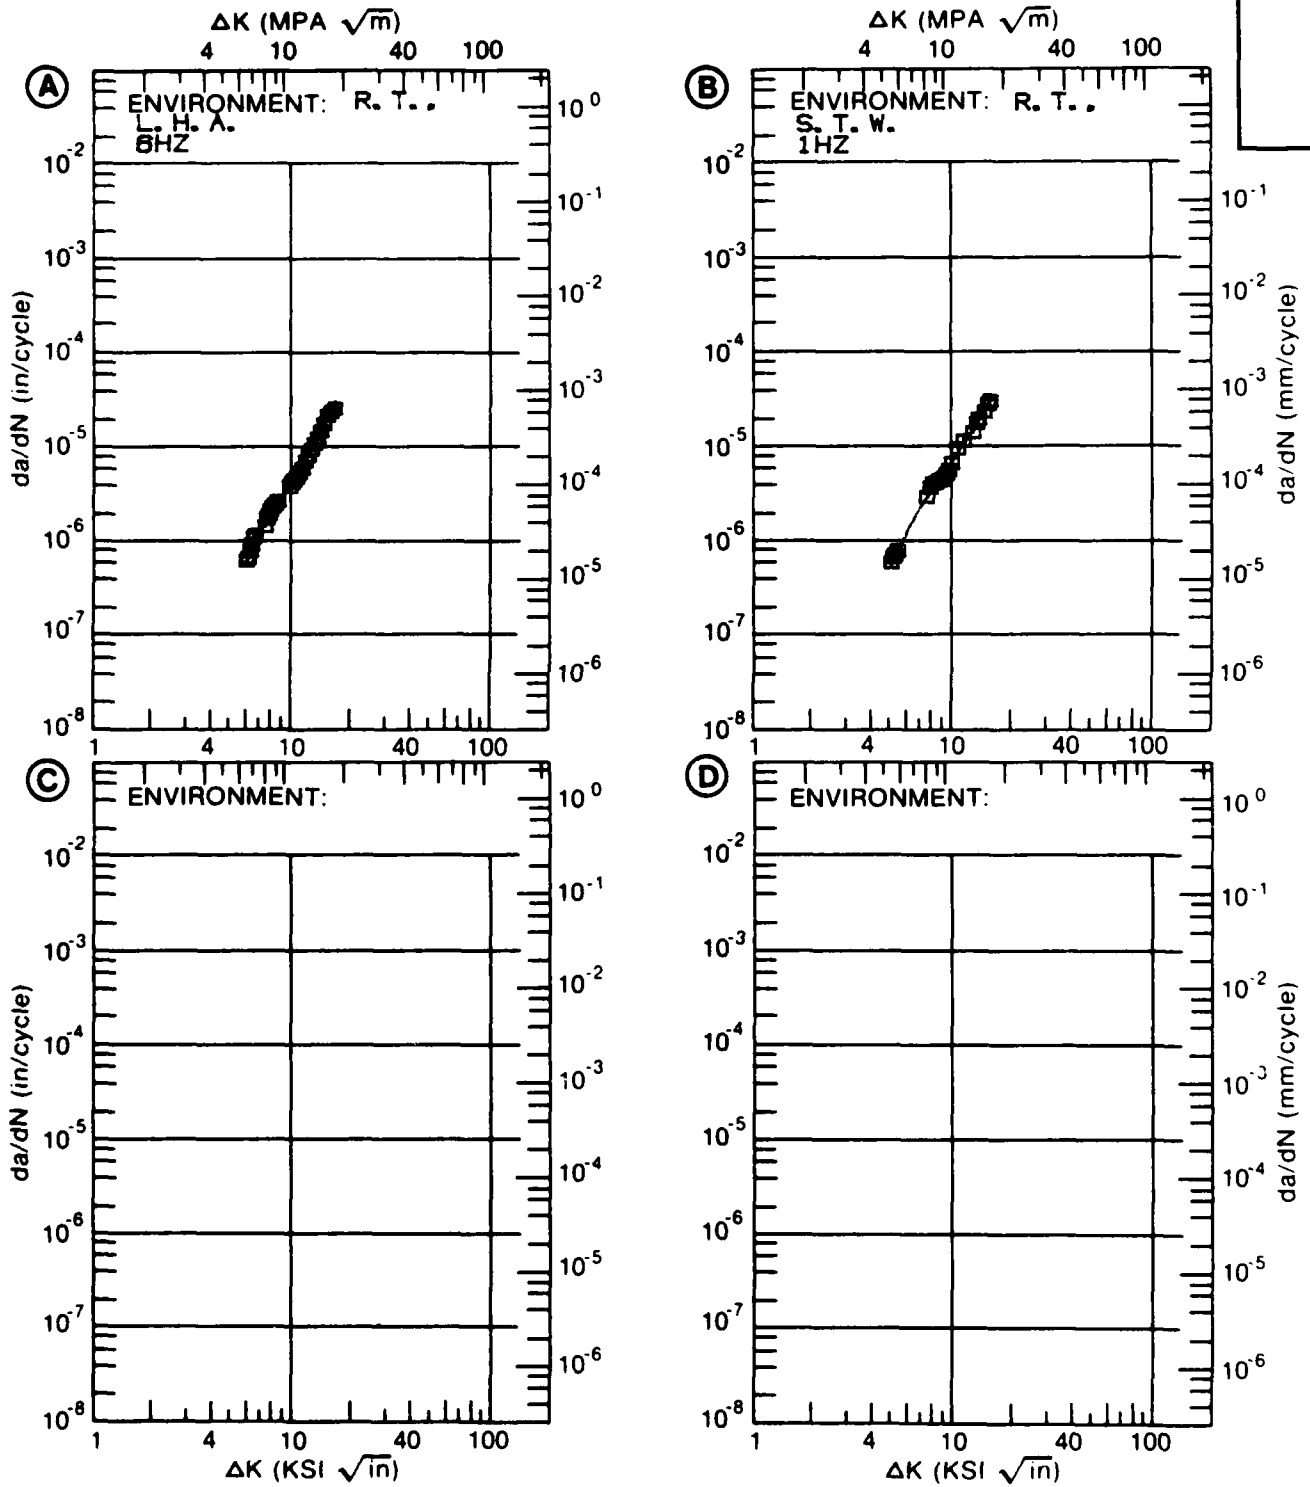


Figure 7.10.3.31

TABLE 7.10.3.32

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.32 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2219
CONDITION: T852
ENVIRONMENT: R. T. , L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K MIN	A: 6.55	1.29			
	B:				
	C:				
	D:				
	7.00	1.36			
	8.00	1.58			
	9.00	1.90			
	10.00	2.35			
	13.00	5.00			
DELTA K MAX	A: 14.88	8.55			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 18.44
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T852
 FORM: 6.00" TH BILLET
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 50.0 KSI
 ULT. STRENGTH: 65.0 KSI
 SPECIMEN THK: 0.997"
 SPECIMEN WIDTH: 6.190"
 REFERENCES: 85837

ALUM. ALLOY
2219

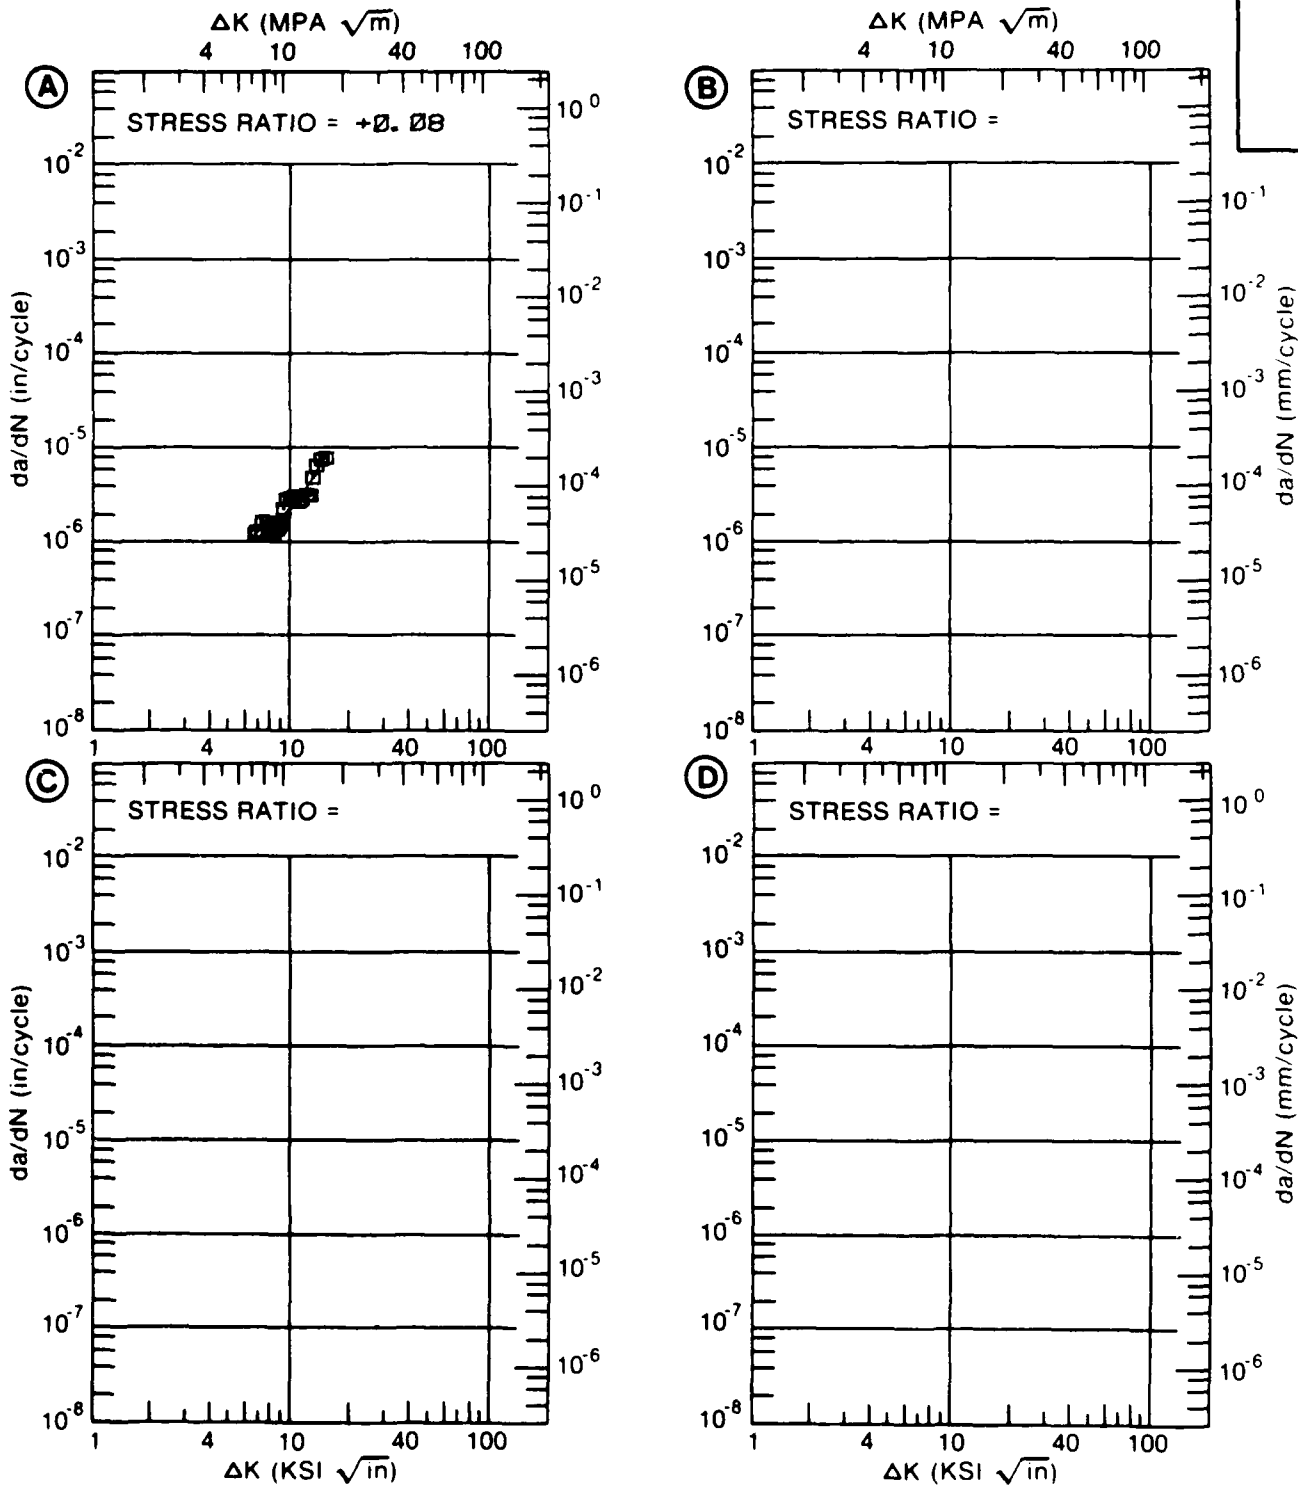


Figure 7.10.3.32

TABLE 7.10.3.33

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.33 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T.		E= R. T.	
		DRY AIR, 2-20HZ		S. T. W., 20HZ	
DELTA K	A: 5.73	.518			
MIN	B: 5.20		1.60		
	C:				
	D:				
	6.00	.633	2.38		
	7.00	1.25	3.70		
	8.00	2.22	5.42		
	9.00	3.63	7.58		
	10.00	5.49	10.2		
	13.00	13.3	20.1		
	16.00	21.6	32.2		
	20.00	27.7			
DELTA K	A: 20.09	27.7			
MAX	B: 16.06		32.4		
	C:				
	D:				
ROOT MEAN SQUARE		24.73	16.63		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T852
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY:

YIELD STRENGTH: 50.7 KSI
 ULT. STRENGTH: 65.0 KSI
 SPECIMEN THK: 0.750- 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL001

ALUM.
ALLOY

2219

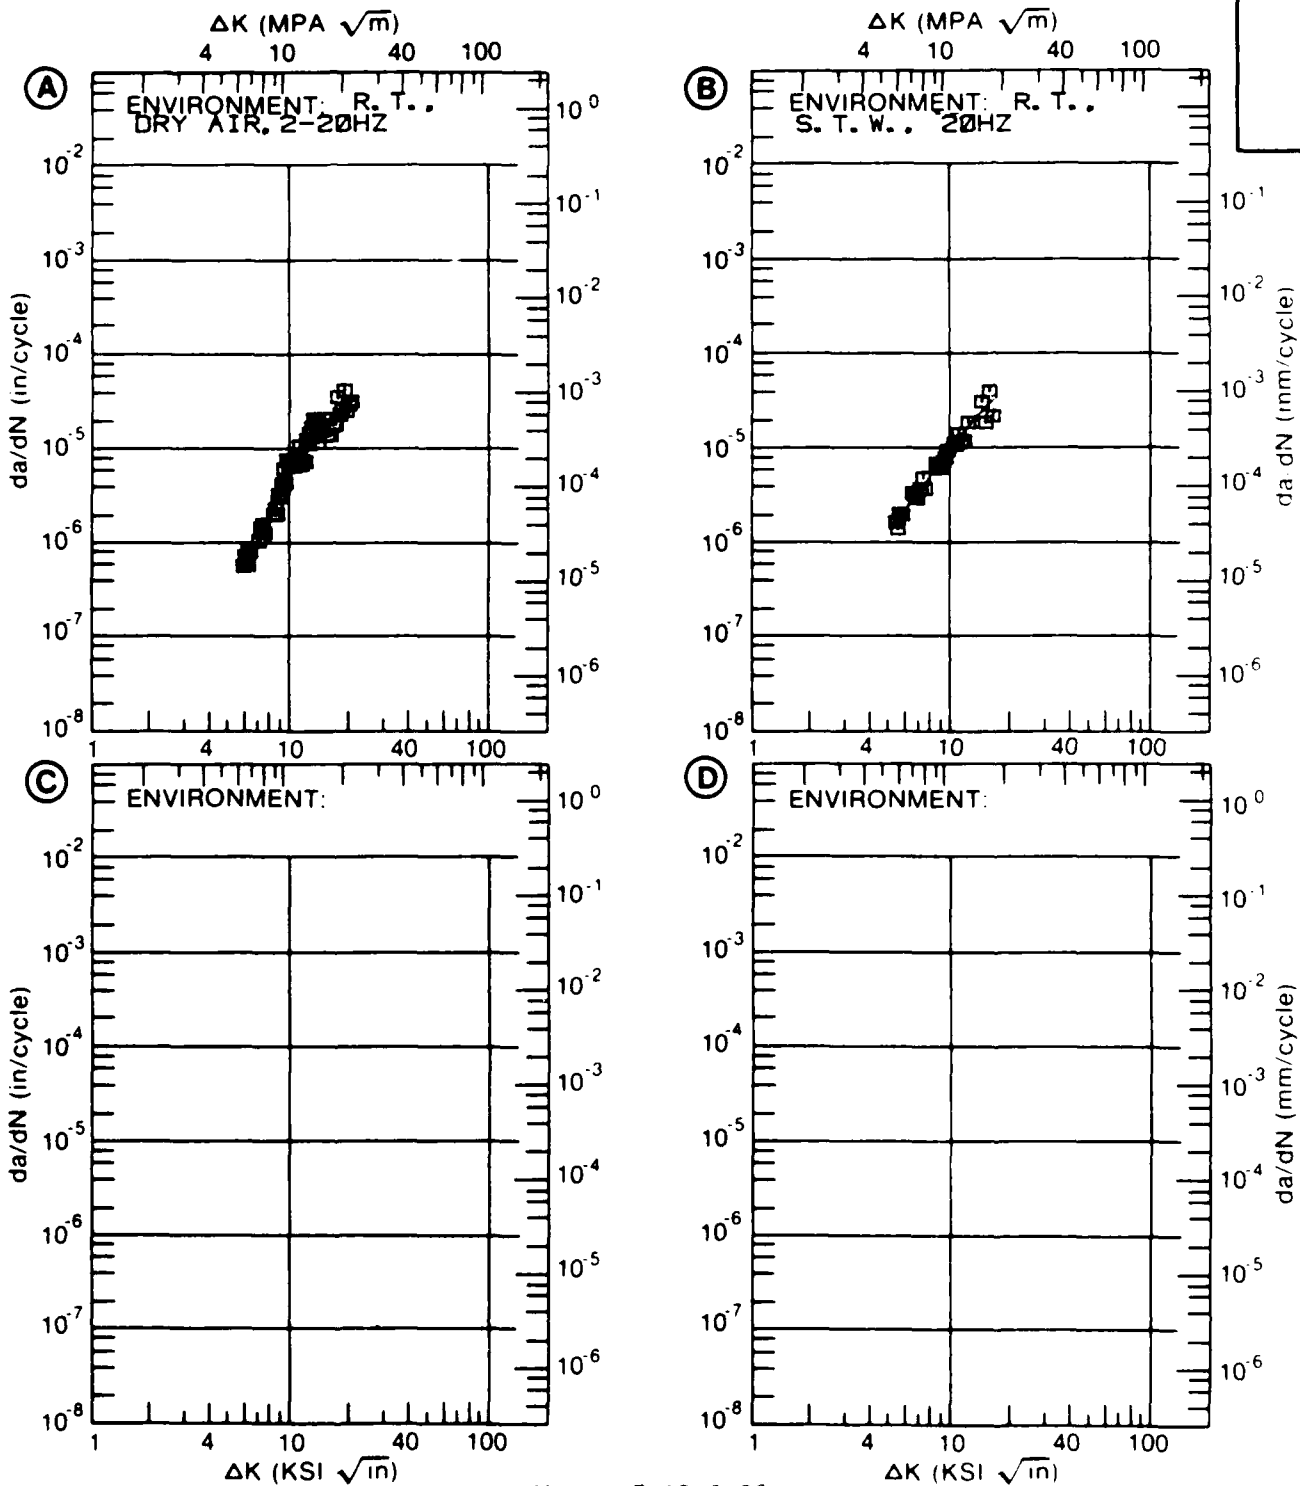


Figure 7.10.3.33

TABLE 7.10.3.34

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.34 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. S. T. W.	
DELTA K	A: 5.72	.560			
MIN	B: 5.75		.963		
	C: 5.70			1.96	
	D:				
	6.00	.762	1.17	2.28	
	7.00	1.75	2.20	3.54	
	8.00	3.10	3.63	5.13	
	9.00	4.84	5.58	7.17	
	10.00	7.08	8.32	9.83	
	13.00	20.8	26.8	24.3	
	16.00	69.7	92.8	59.8	
	20.00	480.		204.	
DELTA K	A: 20.32	568.			
MAX	B: 19.72		500.		
	C: 20.69			253.	
	D:				
ROOT MEAN SQUARE		27.82	28.49	27.22	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T852
 FORM: 2.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 20.00 HZ

YIELD STRENGTH: 50.6 KSI
 ULT. STRENGTH: 66.5 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL001

ALUM. ALLOY
2219

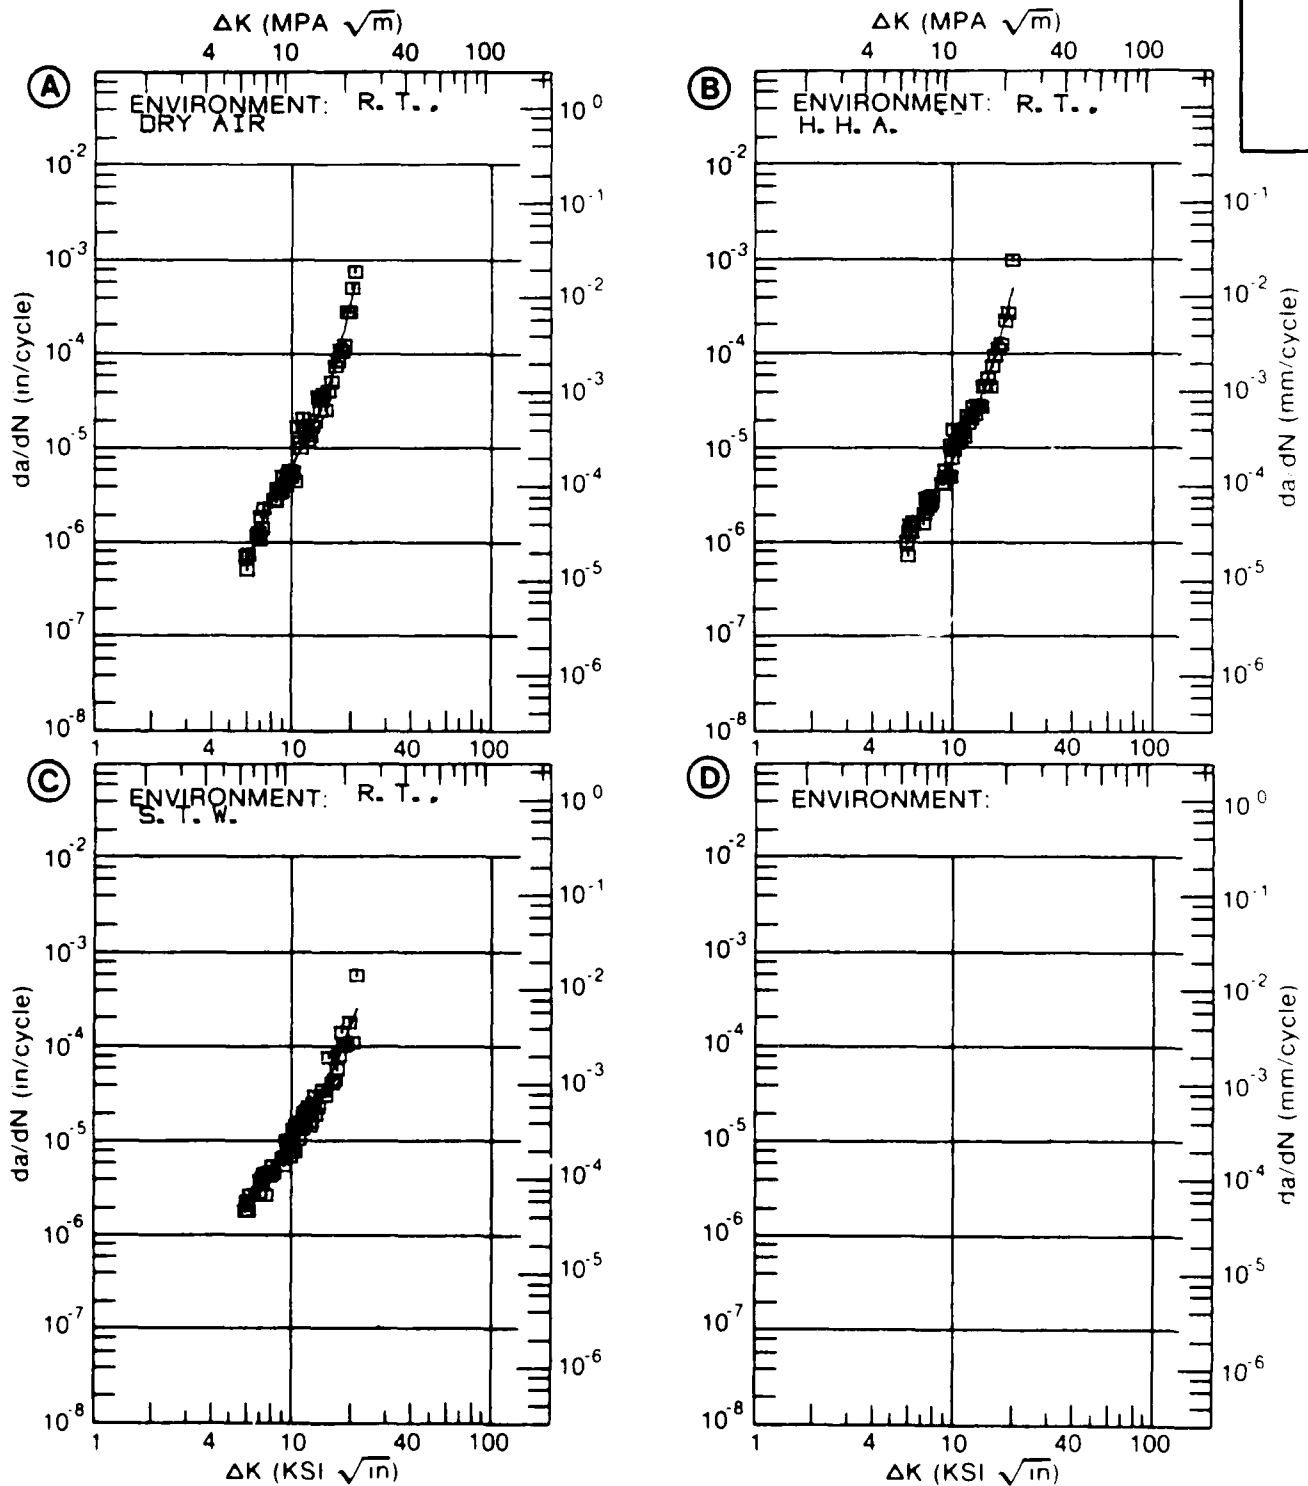


Figure 7.10.3.04

TABLE 7.10.3.35

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.35 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10**6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. : DRY AIR	E= R. T. S. T. W.		
DELTA K MIN	A: 5.69	.482			
	B: 5.69		1.34		
	C:				
	D:				
	6.00	.615	1.64		
	7.00	1.08	2.71		
	8.00	1.53	3.89		
	9.00	1.96	5.09		
	10.00	2.38	6.28		
	13.00	4.01	9.87		
DELTA K MAX	A: 14.60	5.51			
	B: 16.00		13.9		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		12.80	16.11		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0				

CONDITION/HT: T852
 FORM: 5.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 20.00 HZ

YIELD STRENGTH: 49.2 KSI
 ULT. STRENGTH: 62.5 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL001

ALUM.
ALLOY

2219

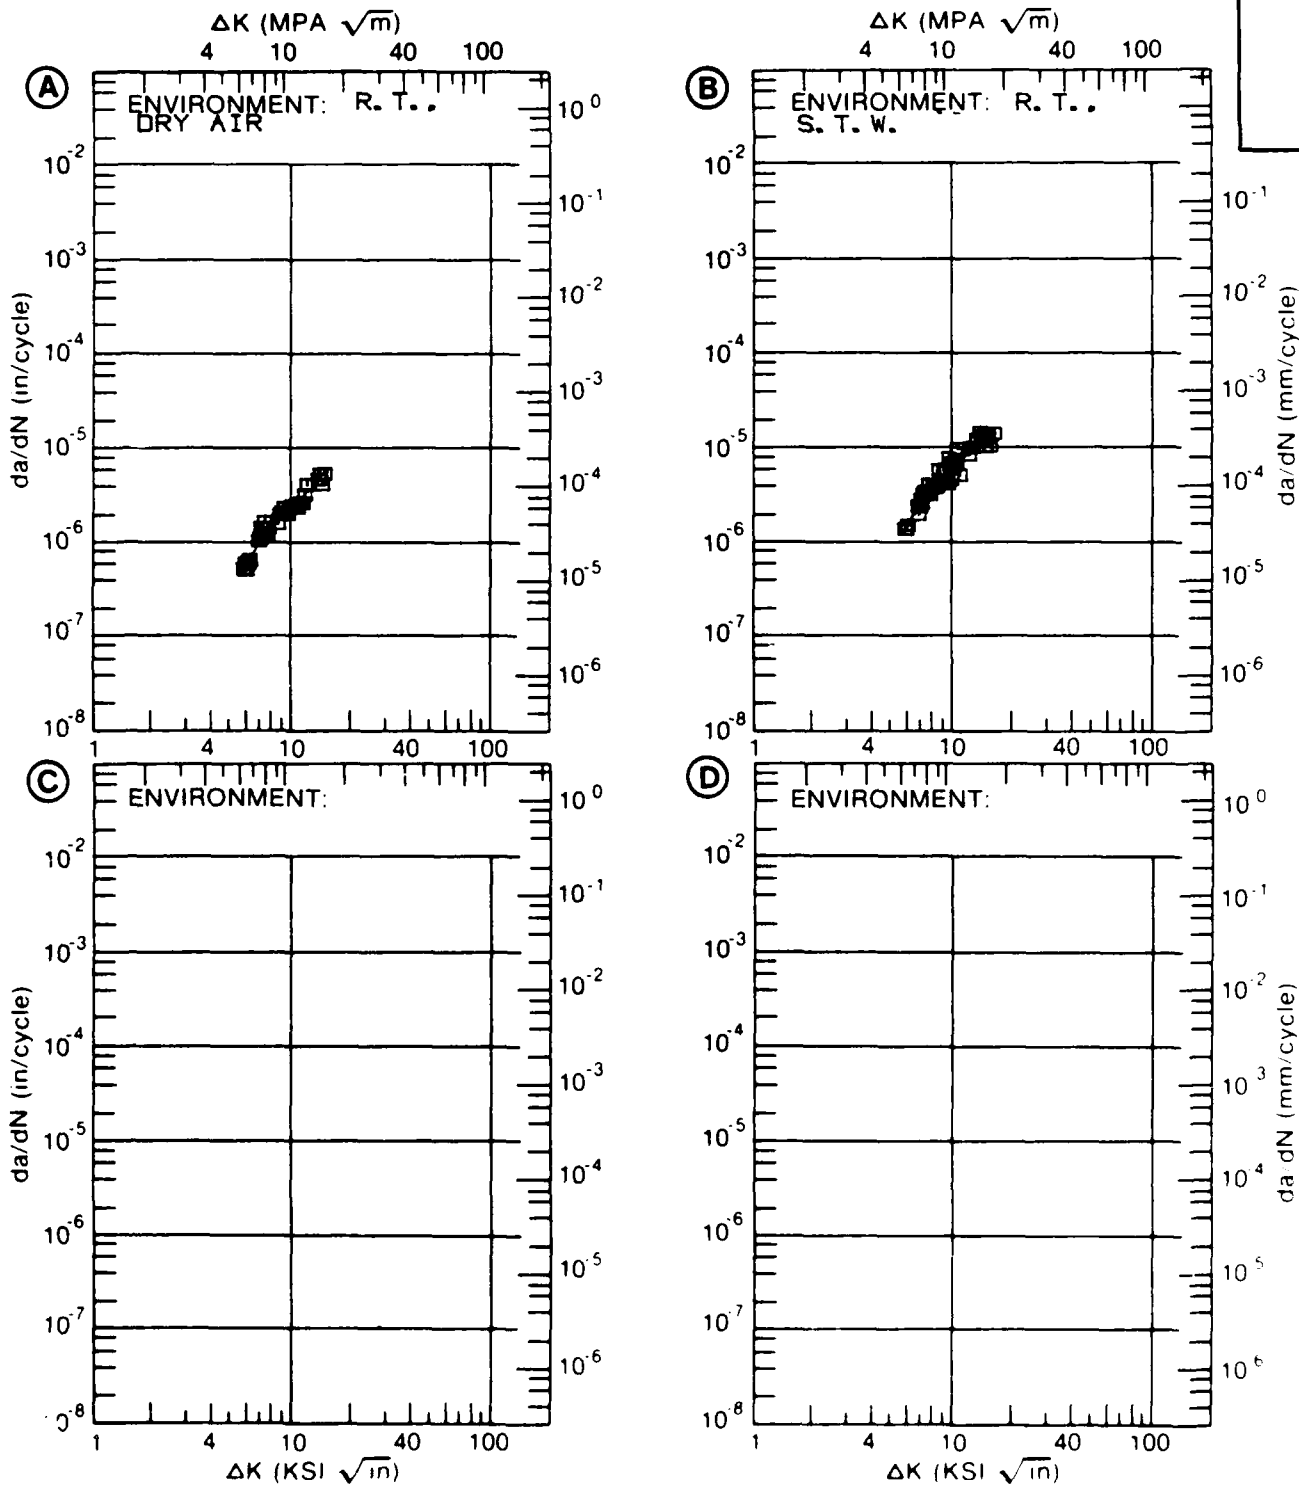


Figure 7.10.3.5

TABLE 7.10.3.36

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.36 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR, 40HZ	E= R. T. S. T. W., 20HZ		
DELTA K	A: 3.22	.0513			
MIN	B: 9.03		6.82		
	C:				
	D:				
	3.50	.0854			
	4.00	.165			
	5.00	.363			
	6.00	.599			
	7.00	.920			
	8.00	1.43			
	9.00	2.32			
	10.00	3.97	10.3		
	13.00	23.3	32.2		
	16.00	138.			
DELTA K	A: 17.51	250.			
MAX	B: 15.40		53.6		
	C:				
	D:				
ROOT MEAN SQUARE		29.30	20.39		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T852
 FORM: 5.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY:

YIELD STRENGTH: 46.4 KSI
 ULT. STRENGTH: 61.6 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: AL001

ALUM.
ALLOY

2219

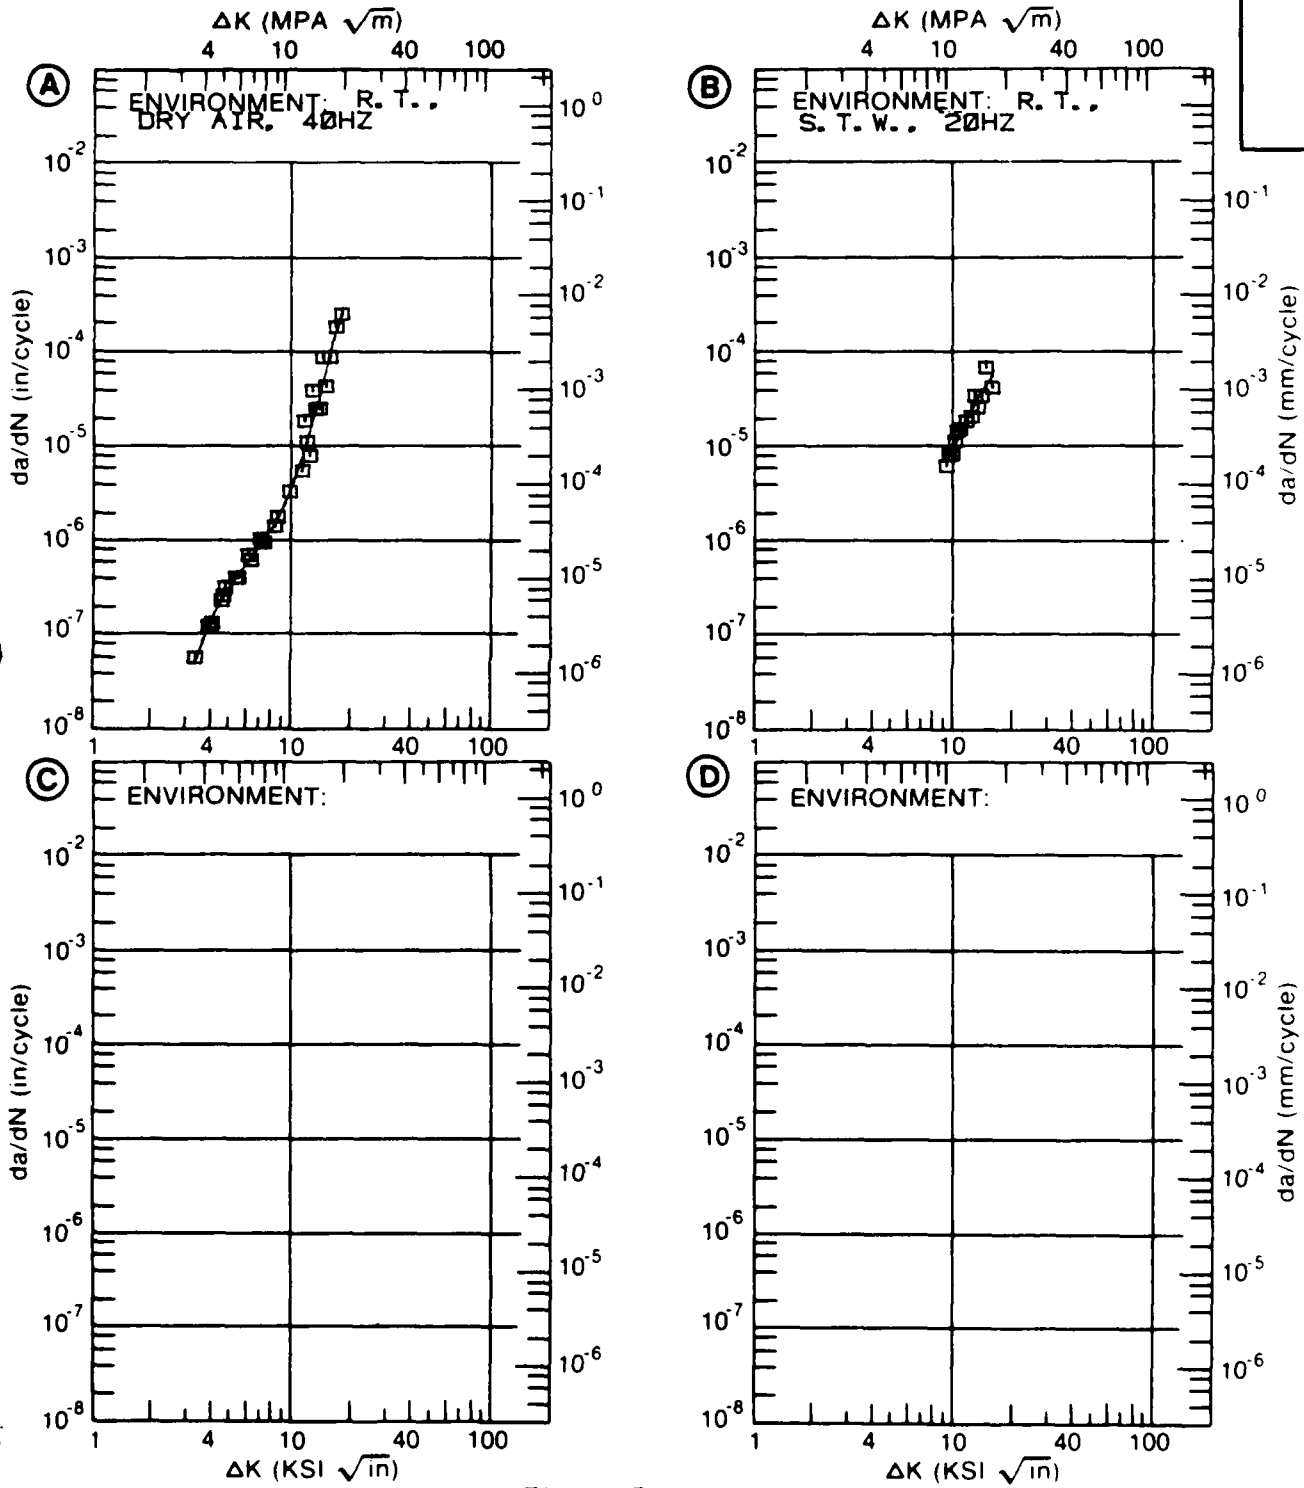


Figure 7.10.3.36

TABLE 7.10.3.37

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.37 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. : DRY AIR	E= R. T. H. H. A.	E= R. T. S. T. W.	
DELTA K	A: 5.69	.708			
MIN	B: 5.75		1.50		
	C: 5.61			2.40	
	D:				
	6.00	.956	1.84	3.15	
	7.00	1.89	3.44	5.25	
	8.00	3.00	5.55	7.74	
	9.00	4.48	8.51	11.1	
	10.00	6.78	13.0	16.5	
	13.00	34.2	56.2	74.1	
	16.00	340.		670.	
DELTA K	A: 16.06	359.			
MAX	B: 15.13		197.		
	C: 16.29			1021.	
	D:				
ROOT MEAN SQUARE		30.43	23.20	18.36	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T852
 FORM: 5.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 20.00 HZ

YIELD STRENGTH: 46.4 KSI
 ULT. STRENGTH: 61.6 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL001

ALUM.
ALLOY

2219

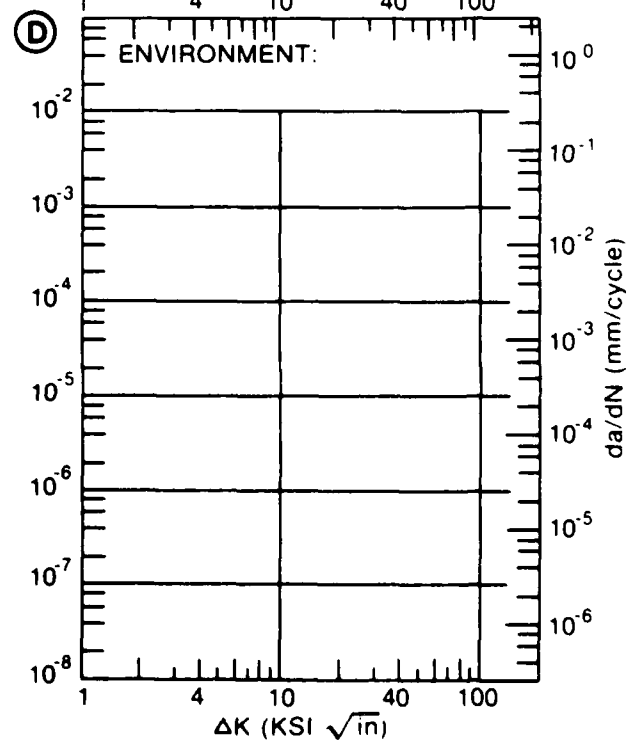
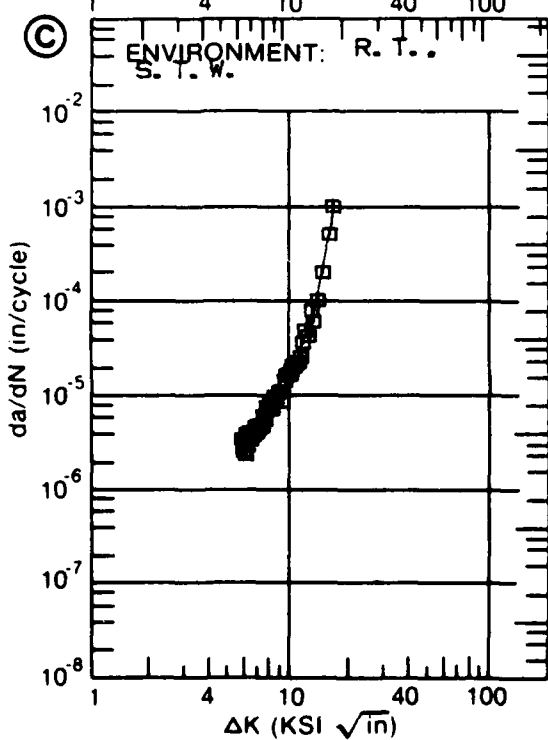
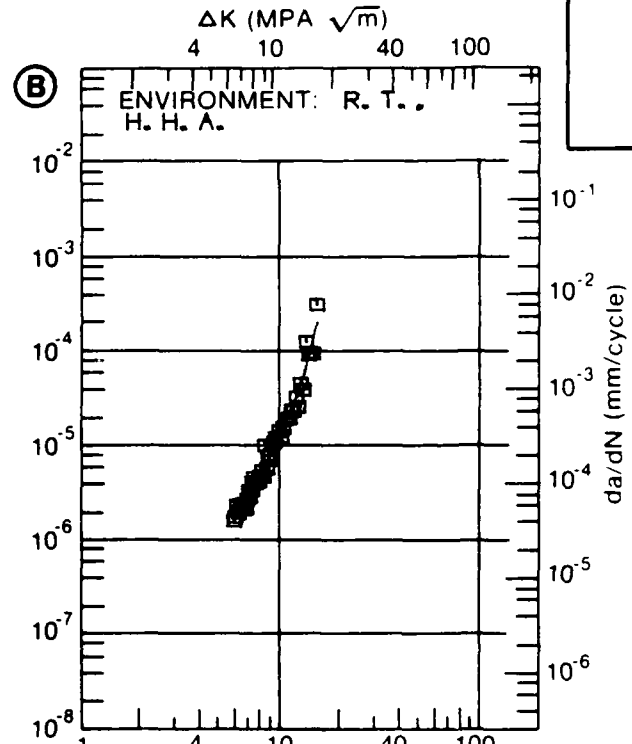
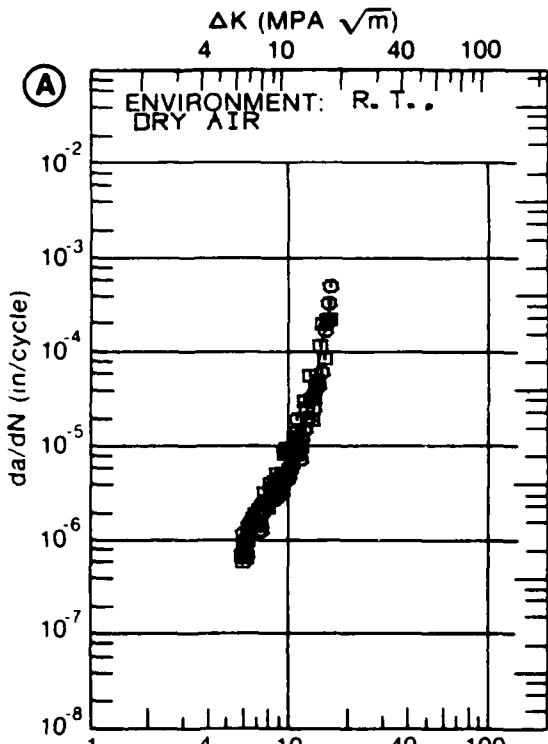


Figure 7.10.3.37

TABLE 7.10.3.38

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.38 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2219			
CONDITION: T852					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. S. T. W.	
DELTA K MIN	A: 5.73	.915			
	B: 5.75		1.40		
	C: 5.72			2.15	
	D:				
	6.00	1.19	1.88	2.91	
	7.00	2.29	4.19	5.89	
	8.00	3.46	6.71	8.78	
	9.00	4.93	9.56	12.0	
	10.00	7.32	13.5	16.6	
	13.00	41.9	54.7	74.6	
	16.00		477.		
DELTA K MAX	A: 15.83	517.			
	B: 16.06		502.		
	C: 15.97			835.	
	D:				
ROOT MEAN SQUARE		30.74	25.21	27.85	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0				

CONDITION/HT: T852
 FORM: 5.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: +0.33
 FREQUENCY: 2.00- 20.00 HZ

YIELD STRENGTH: 47.2 KSI
 ULT. STRENGTH: 62.3 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH:
 REFERENCES: AL001

ALUM.
ALLOY

2219

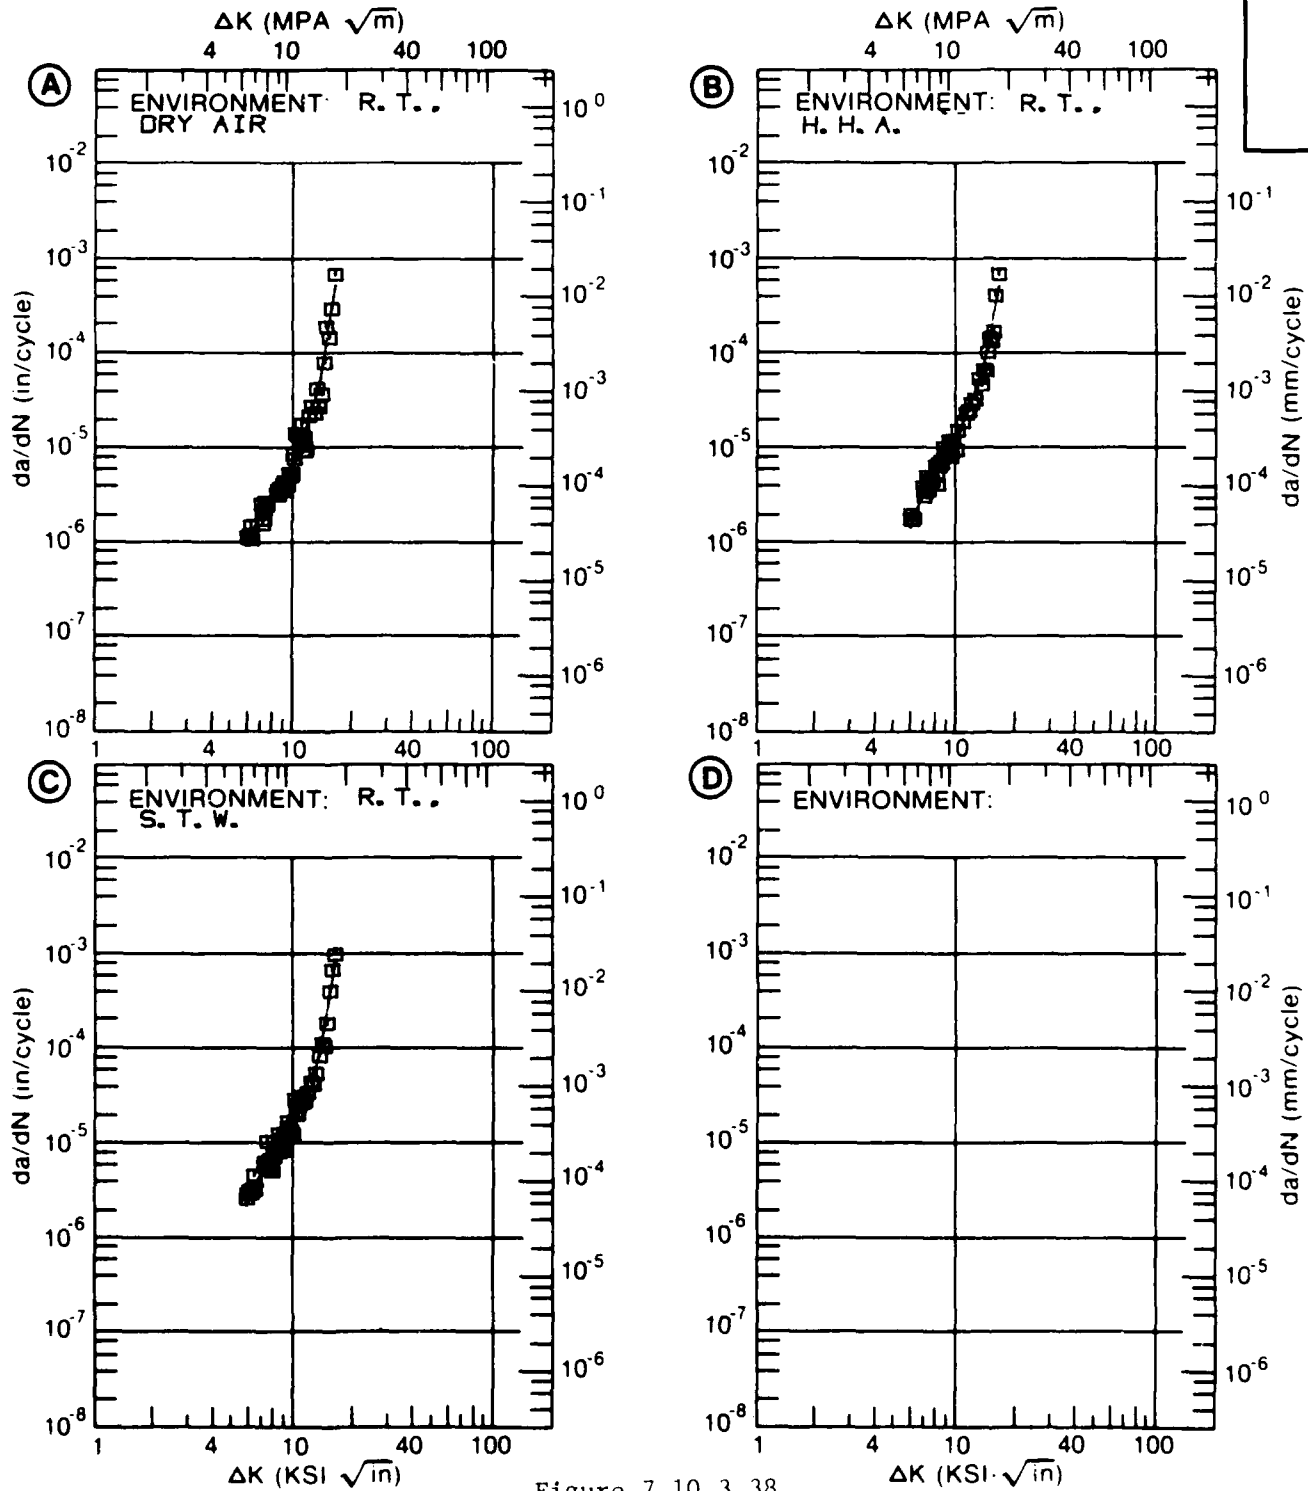


Figure 7.10.3.38

TABLE 7.10.3.39

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.10.3.39 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 2219
CONDITION: T37

K MAX (KSI*IN**1/2)	DA/DT (10** ⁻⁶ IN/HOUR)			
	A	B	C	D
	E- WET 3X/DAY WITH 3 5% NACL			
A: 20.00	411.			
B:				
C:				
D:				
25.00	661.			
30.00	917.			
35.00	1171.			
40.00	1423.			
50.00	1933.			
60.00	2474.			
70.00	3075.			
A: 80.00	3764.			
B:				
C:				
D:				

ROOT MEAN SQUARE 2.84
PERCENT ERROR

CONDITION/HT: T37
 FORM: 1.5" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: S-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 CRACK LENGTH (A_0):
 K_{ISCC} :
 REFERENCES: 78313

ALUM.
ALLOY

2219

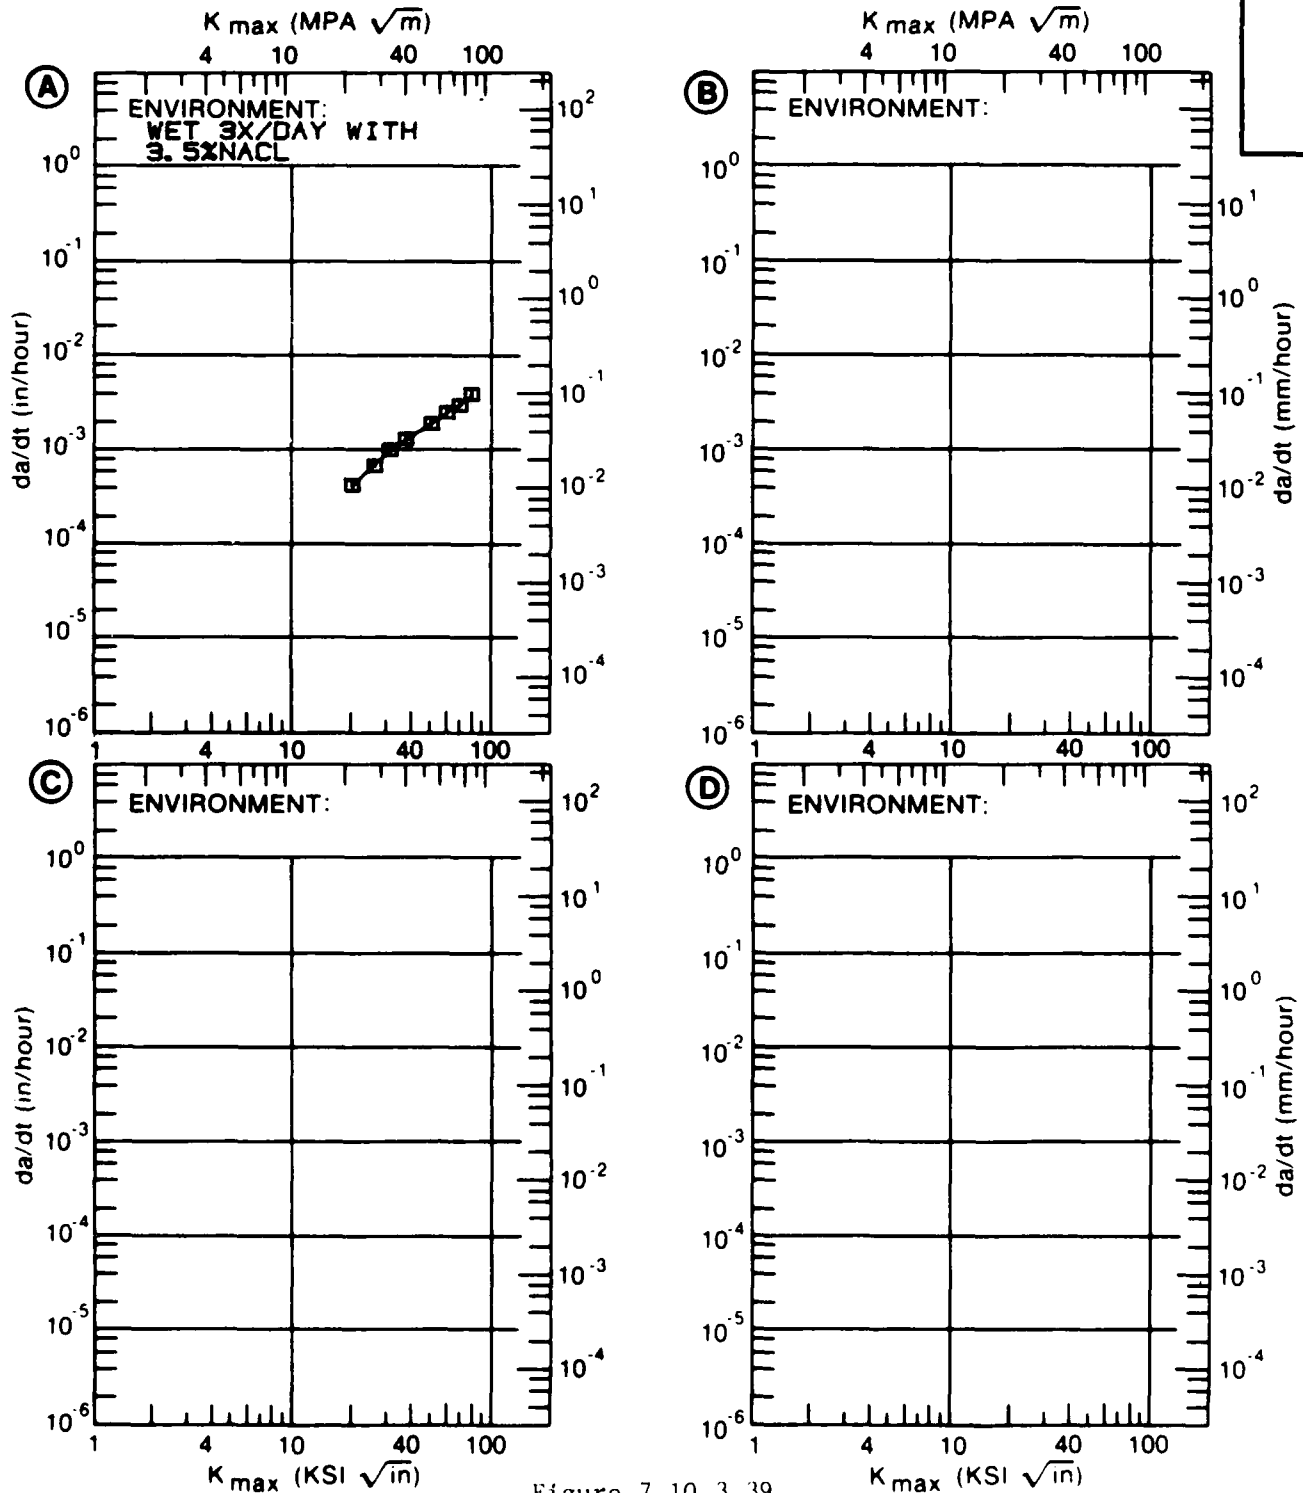


Figure 7.10.3.39

Table 7.10.3.40

CONDITION	--PRODUCT--		TEST SPEC OR STR	YIELD (KSI)	ENVIRONMENT	ALUMINUM		2219		K (ISCC)		STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)	DESIGN (IN)	LENGTH (IN)	CRACK (KBI+SBRT IN)	MEAN			
T37	P	2.00	R.T.	S-L	42.1	INDUSTRIAL ATM	2.000	1.000	CT	27.10	13.00			1973 86688
T37	P	2.00	R.T.	S-L	42.1	SALT-DICHR-O-MATE-ACETATE	2.000	1.000	CT	27.10	9.00			1973 86688
T37	P	2.00	R.T.	S-L	42.1	SEACOAST ATM	2.000	1.000	CT	27.10	13.00			1973 86688
T851	P	1.75	R.T.	L-T	50.0	F.C.S.	5.500	1.000	DCB	32.00	30.50	29.0/	2.1	75240 1976 R1006 75240 1976 R1006
T851	P	1.75	R.T.	L-T	50.0	S.C.S.	5.500	1.000	DCB	32.00	27.00			75240 1976 R1006 59100 1976 R1006 61680 1976 R1006
T851	P	1.75	R.T.	L-T	50.0	S.T.W.	5.500	1.000	DCB	32.00	36.00	34.3/	6.4	51720 1976 R1006 83520 1976 R1006 51720 1976 R1006
T851	P	1.75	R.T.	T-L	48.0	S.T.W.	5.500	1.000	DCB	30.00	27.00			51720 1976 R1006
T851	P	1.75	R.T.	S-L	---	S.T.W.	5.500	1.000	DCB	30.00	29.50			83520 1976 R1006 51720 1976 R1006
T851	P	1.00	R.T.	S-L	58.0	3.5 PCT NACL	4.000	1.000	DCB	27.00	18.00			1968 84331
T87	P	2.00	R.T.	S-L	57.7	INDUSTRIAL ATM	2.000	1.000	CT	19.60	19.00			1973 86688
T87	P	2.00	R.T.	S-L	57.7	SALT-DICHR-O-MATE-ACETATE	2.000	1.000	CT	19.60	19.00			1973 86688
T87	P	2.00	R.T.	S-L	57.7	SEACOAST ATM	2.000	1.000	CT	19.60	19.00			1973 86688

TABLE 7.11.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.11.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 2324
CONDITION: T39
ENVIRONMENT: R. T., H. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.33			
DELTA K	A: 2.65	.0344			
MIN	B:				
	C:				
	D:				
	3.00	.0994			
	3.50	.178			
	4.00	.222			
	5.00	.462			
	6.00	1.30			
	7.00	2.72			
	8.00	4.66			
	9.00	7.09			
	10.00	10.0			
	13.00	23.2			
DELTA K	A: 14.47	33.7			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 15.79
PERCENT ERROR

LIFE	0.0-0.5	
PREDICTION	0.5-0.8	1
RATIO	0.8-1.25	2
SUMMARY	1.25-2.0	
(NP/NA)	>2.0	

CONDITION/HT: T39
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 FREQUENCY: 25.00
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.249- 0.251"
 SPECIMEN WIDTH: 2.500- 2.547"
 REFERENCES: AL011

ALUM. ALLOY
2324

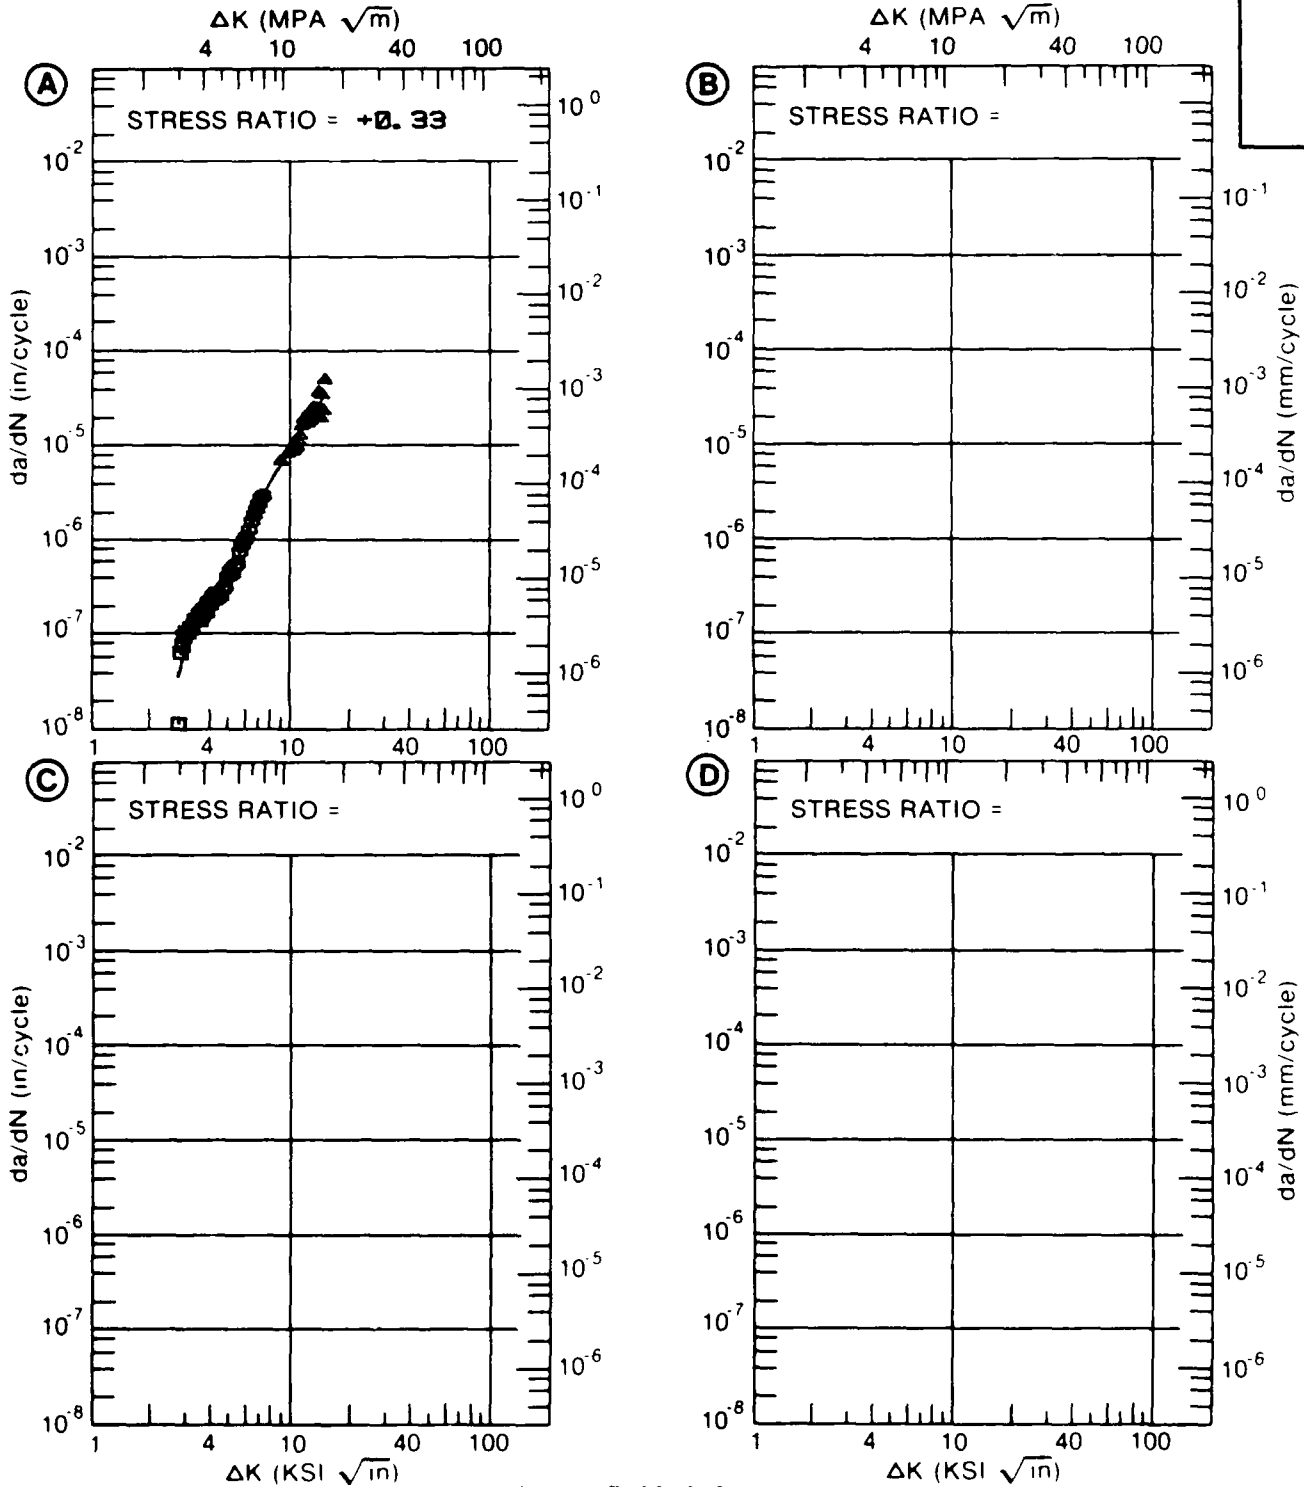


Figure 7.11.3.1

Table 7.12.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 2419 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD DEVIATION (KSI √IN)	PLATE	(NUMBER OF SPECIMENS)
T851	42.6 ± 5.3 (23)	I-I	37 2 + 4 2 (92)
		S-I	24 8 ± 2 5 (3)

Table 7.12.2.1

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	SPECIMEN		CRACK LENGTH (IN)	K(IC) (IN)	2.5* K(IC)/TYS)**2 (IN)	K(IC) MEAN (IN)	STAN DEV (IN)	DATE	REFER								
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)								DESIGN							
T851	P	2.55	50.1	R.T.	L-T	6.017	2.506	CT	3.129	2.40	49.10		1978	MPC01								
															2.55	5.959	2.583	CT	3.158	1.98	44.60	
															2.90	50.5	6.057	2.945	CT	3.089	2.11	46.90
															2.90	50.7	6.053	2.900	CT	3.087	1.84	43.90
															2.90	50.8	6.041	2.897	CT	3.081	1.98	45.50
															2.90	51.1	6.052	2.905	CT	3.026	1.44	39.20
															2.90	51.4	6.020	2.947	CT	3.070	1.60	41.30
															2.00	51.7	4.000	2.000	CT	---	1.17	35.30
															2.00	51.7	4.000	2.000	CT	---	1.09	34.20
															2.00	51.7	4.000	2.000	CT	---	1.14	34.90
															2.55	52.1	3.026	1.501	CT	1.913	1.29	38.00
															2.90	52.1	5.962	2.934	CT	3.100	2.30	50.20
															2.90	52.2	5.967	2.937	CT	3.103	2.16	48.90
															2.90	52.4	5.033	2.375	CT	2.567	1.68	43.00
															2.50	52.7	5.998	2.519	CT	3.059	1.64	43.00
															2.50	53.0	6.059	2.598	CT	3.090	2.50	53.00
															3.00	53.2	4.034	1.999	CT	2.017	1.36	39.70
															3.00	53.2	4.035	1.999	CT	2.058	1.44	40.70
															2.90	53.4	4.951	2.374	CT	2.624	1.84	46.40
															2.90	53.8	4.992	1.790	CT	2.596	1.19	36.90
2.90	54.0	6.025	2.933	CT	3.193	1.98	48.90															
2.90	54.9	5.019	1.750	CT	2.610	1.26	39.00															
2.90	55.8	5.006	1.750	CT	2.603	1.19	38.60															
T851	P	2.00	47.6	200	L-T	4.000	2.000	CT	---	1.19	32.90		1975	UD004								
															2.00	4.000	2.000	CT	---	1.11	31.70	
															2.00	4.000	2.000	CT	---	1.17	32.60	
T851	P	2.00	43.8	300	L-T	4.000	2.000	CT	---	1.33	31.90		1975	UD004								
															2.00	4.000	2.070	CT	---	1.35	32.20	
															2.00	4.000	2.000	CT	---	1.32	31.80	
T851	P	1.75	46.8	R.T.	T-L	5.053	1.761	CT	2.567	1.48	36.30		1978	MPC01								
															1.75	5.012	1.758	CT	2.555	1.40	35.70	
															1.75	47.0	2.991	1.399	CT	1.589	1.19	32.80
															1.75	47.2	4.994	1.762	CT	2.597	1.52	37.10
															1.75	47.4	3.019	1.397	CT	1.570	1.29	34.20
1.75	47.4	4.994	1.757	CT	2.597	1.52	37.10															
1.75	47.4	4.985	1.761	CT	2.592	1.52	37.00															

Table 7.12.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEMP (F)	R. T.	T-L	SPECIMEN		K(1C)	2.5* K(1C)/TYB)**2	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
	PRODUCT-- FORM	THICK (IN)						THICK (IN)	DESIGN						
T891	P	1.75	5.004	47.6			CT	1.762	2.602	1.60	38.10			1978	MPC01
		1.75	2.994	47.6			CT	1.397	1.587	1.29	34.70			1978	MPC01
		1.75	4.987	47.6			CT	1.762	2.593	1.60	38.20			1978	MPC01
		1.75	2.995	47.7			CT	1.398	1.587	1.12	32.10			1978	MPC01
		1.75	4.975	47.7			CT	1.759	2.987	1.36	35.70			1978	MPC01
		2.55	4.998	49.0			CT	2.401	2.649	2.11	45.30			1978	MPC01
		1.75	2.981	49.0			CT	1.402	1.550	1.29	35.30			1978	MPC01
		2.90	6.000	49.2			CT	2.951	3.180	1.84	42.40			1978	MPC01
		2.90	6.028	49.4			CT	2.900	3.195	1.48	38.20			1978	MPC01
		2.90	6.019	49.4			CT	2.896	3.130	2.20	46.50			1978	MPC01
		2.00	2.996	49.7			CT	1.402	1.558	0.99	31.80			1978	MPC01
		2.90	4.982	49.9			CT	2.374	2.690	1.60	40.40			1978	MPC01
		2.90	6.000	50.1			CT	2.940	3.180	1.84	43.30			1978	MPC01
		2.55	5.004	50.3			CT	2.401	2.652	1.68	41.50			1978	MPC01
		2.90	6.014	50.5			CT	2.912	3.067	1.08	33.70			1978	MPC01
		2.90	5.051	50.7			CT	1.747	2.976	1.56	40.30			1978	MPC01
		2.90	6.047	50.9			CT	2.931	3.205	1.56	40.40			1978	MPC01
		2.90	5.946	51.0			CT	2.937	3.092	1.22	36.10			1978	MPC01
		2.90	4.989	51.0			CT	1.747	2.994	1.72	42.40			1978	MPC01
		2.55	3.015	51.1			CT	1.500	1.568	1.15	34.80			1978	MPC01
		2.90	4.989	51.2			CT	2.375	2.644	1.36	38.00			1978	MPC01
		3.00	4.026	51.2			CT	1.996	2.053	0.78	29.10			1978	MPC01
		2.50	6.049	51.2			CT	2.511	3.085	1.68	42.30			1978	MPC01
		3.00	4.016	51.2			CT	1.999	2.048	0.78	29.10			1978	MPC01
		2.90	5.043	51.4			CT	1.746	2.972	1.48	40.00			1978	MPC01
		2.50	5.992	51.4			CT	2.534	3.166	1.44	39.40			1978	MPC01
		3.00	3.022	51.6			CT	1.403	1.541	1.22	36.50			1978	MPC01
		2.90	3.029	52.1			CT	1.747	2.969	1.72	43.40			1978	MPC01
		3.00	3.983	52.3			CT	1.999	2.071	1.08	34.90			1978	MPC01
		3.00	3.979	52.3			CT	1.999	2.069	1.19	36.50			1978	MPC01
		2.55	5.968	52.3			CT	2.501	3.163	1.12	35.10			1978	MPC01
		2.00	4.000	52.5			CT	2.000	2.000	0.89	30.60			1975	UD004
2.90	5.026	52.5			CT	1.746	2.563	1.68	43.10			1978	MPC01		
2.00	4.000	52.5			CT	2.000	2.000	0.95	32.30			1975	UD004		
2.90	5.051	52.6			CT	1.748	2.976	1.40	39.60			1978	MPC01		
2.90	4.983	52.8			CT	1.749	2.641	1.12	35.90			1978	MPC01		
2.90	5.048	52.8			CT	1.750	2.625	0.99	33.40			1978	MPC01		
2.55	5.973	52.9			CT	2.461	3.046	1.19	36.60			1978	MPC01		

Table 7.12.2.1 (Con't)

CONDITION	--PRODUCT--		TEST SPECIMEN	YIELD	ALUMINUM		W	SPECIMEN		CRACK	2.5*	K(IIC)	K(IIC) STAN	DATE	REFER
	FORM	THICK			THICK	THICK		LENGTH	(IN)						
	(IN)	(IN)	ORIENT	(KSI)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(IN)	(KSI*SQRT IN)	(KSI*SQRT IN)		
T851	P	2.90	R. T.	53.5	4.998	1.750	CT	2.649	1.08	35.80		35.80		1978	MPC01
		2.90		53.6	5.985	2.937	CT	3.172	1.80	46.00		46.00		1978	MPC01
		2.90		53.6	5.053	1.750	CT	2.577	1.05	35.00		35.00		1978	MPC01
		2.90		53.7	4.977	2.374	CT	2.638	1.26	38.60		38.60		1978	MPC01
		2.55		53.9	3.020	1.498	CT	1.510	0.87	32.10		32.10		1978	MPC01
		2.90		54.6	5.029	1.747	CT	2.569	1.36	40.70	37.2/	4.2	37.2/	4.2	1978
T851	P	2.00	200	47.1	4.000	2.000	CT	---	0.97	29.30		29.30		1975	UD004
		2.00		47.1	4.000	2.000	CT	---	0.94	28.90		28.90		1975	UD004
T851	P	2.00	300	43.2	4.000	2.000	CT	---	1.12	28.90		28.90		1975	UD004
		2.00		43.2	4.000	2.000	CT	---	1.09	28.50	28.7/	0.3	28.7/	0.3	1975
T851	P	2.00	R. T.	51.7	4.000	2.000	CT	---	0.50	23.20		23.20		1975	UD004
		2.00		51.7	4.000	2.000	CT	---	0.49	22.90		22.90		1975	UD004
		2.90		52.4	2.006	1.001	CT	1.023	0.49	22.90		22.90		1975	UD004
		2.90		53.2	1.981	1.001	CT	1.030	0.52	24.20		24.20		1978	MPC01
		2.90		54.4	1.994	1.001	CT	1.037	0.48	23.80		23.80		1978	MPC01
		2.90		54.4	1.994	1.001	CT	1.037	0.60	26.80	24.0/	1.5	24.0/	1.5	1978
T851	P	3.00	R. T.	50.4	1.989	1.000	CT	1.034	0.48	22.90		22.90		1978	MPC01
		3.00		50.4	2.018	0.999	CT	1.029	0.57	24.40		24.40		1978	MPC01
		3.00		51.6	1.994	1.000	CT	0.997	0.70	27.40	24.8/	2.5	24.8/	2.5	1978

TABLE 7.12.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.12.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2419			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 6.26	1.28			
MIN	B:				
	C:				
	D:				
	7.00	2.07			
	8.00	3.01			
	9.00	4.35			
	10.00	6.30			
	13.00	14.7			
	16.00	24.9			
	20.00	53.9			
DELTA K	A: 20.00	53.9			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		18.62			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 51.7 KSI
 ULT. STRENGTH: 66.9 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 1.850"
 REFERENCES: UD004

ALUM. ALLOY
2419

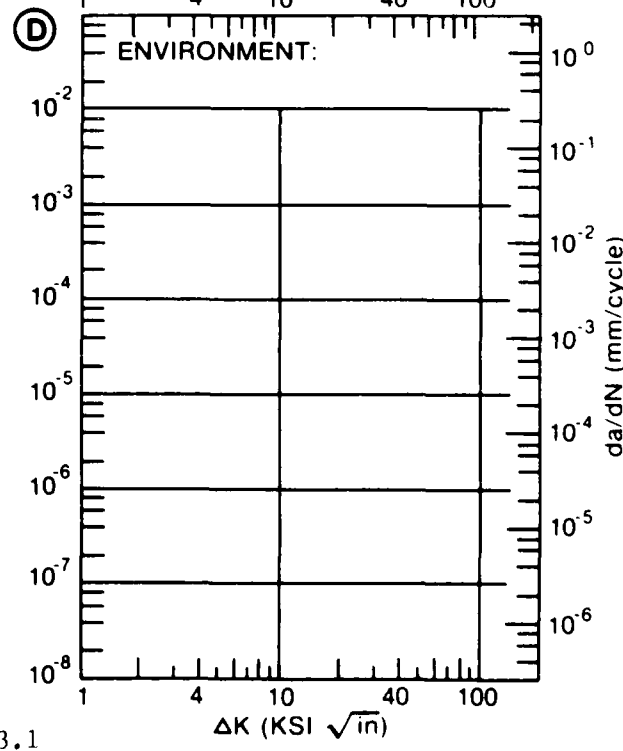
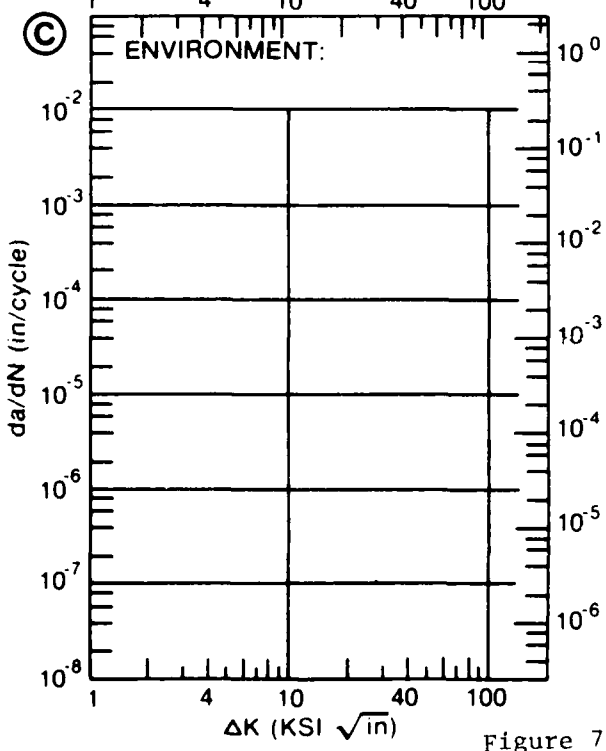
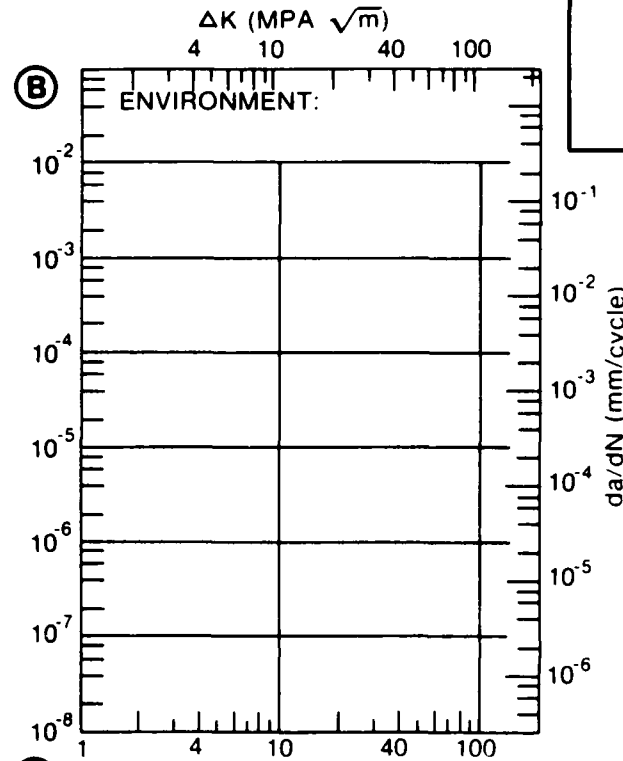
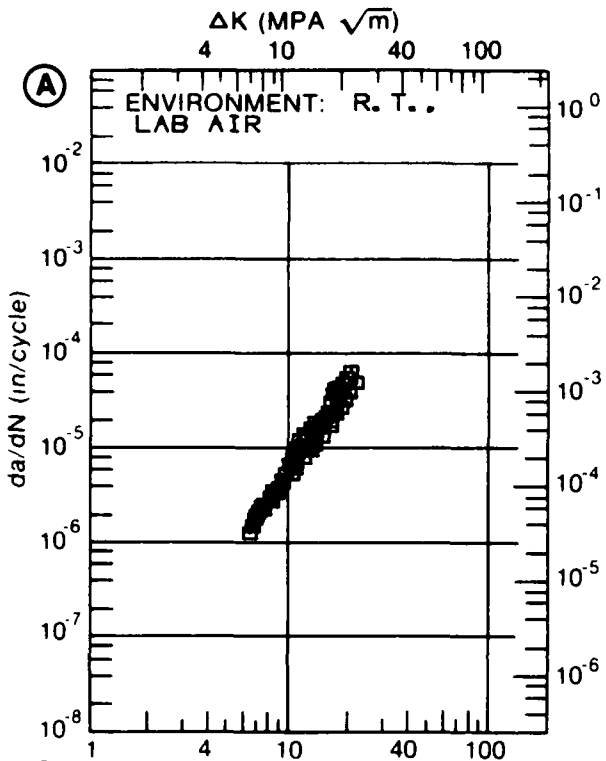


Figure 7.12.3.1

TABLE 7.12.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.12.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2419			
CONDITION: T851					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K	A: 6.39	.906			
MIN	B:				
	C:				
	D:				
	7.00	1.97			
	8.00	2.68			
	9.00	3.94			
	10.00	5.59			
	13.00	10.3			
	16.00	17.1			
DELTA K	A: 17.33	26.1			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		19.15			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T851
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 52.5 KSI
 ULT. STRENGTH: 66.6 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 1.850"
 REFERENCES: UD004

ALUM.
ALLOY

2419

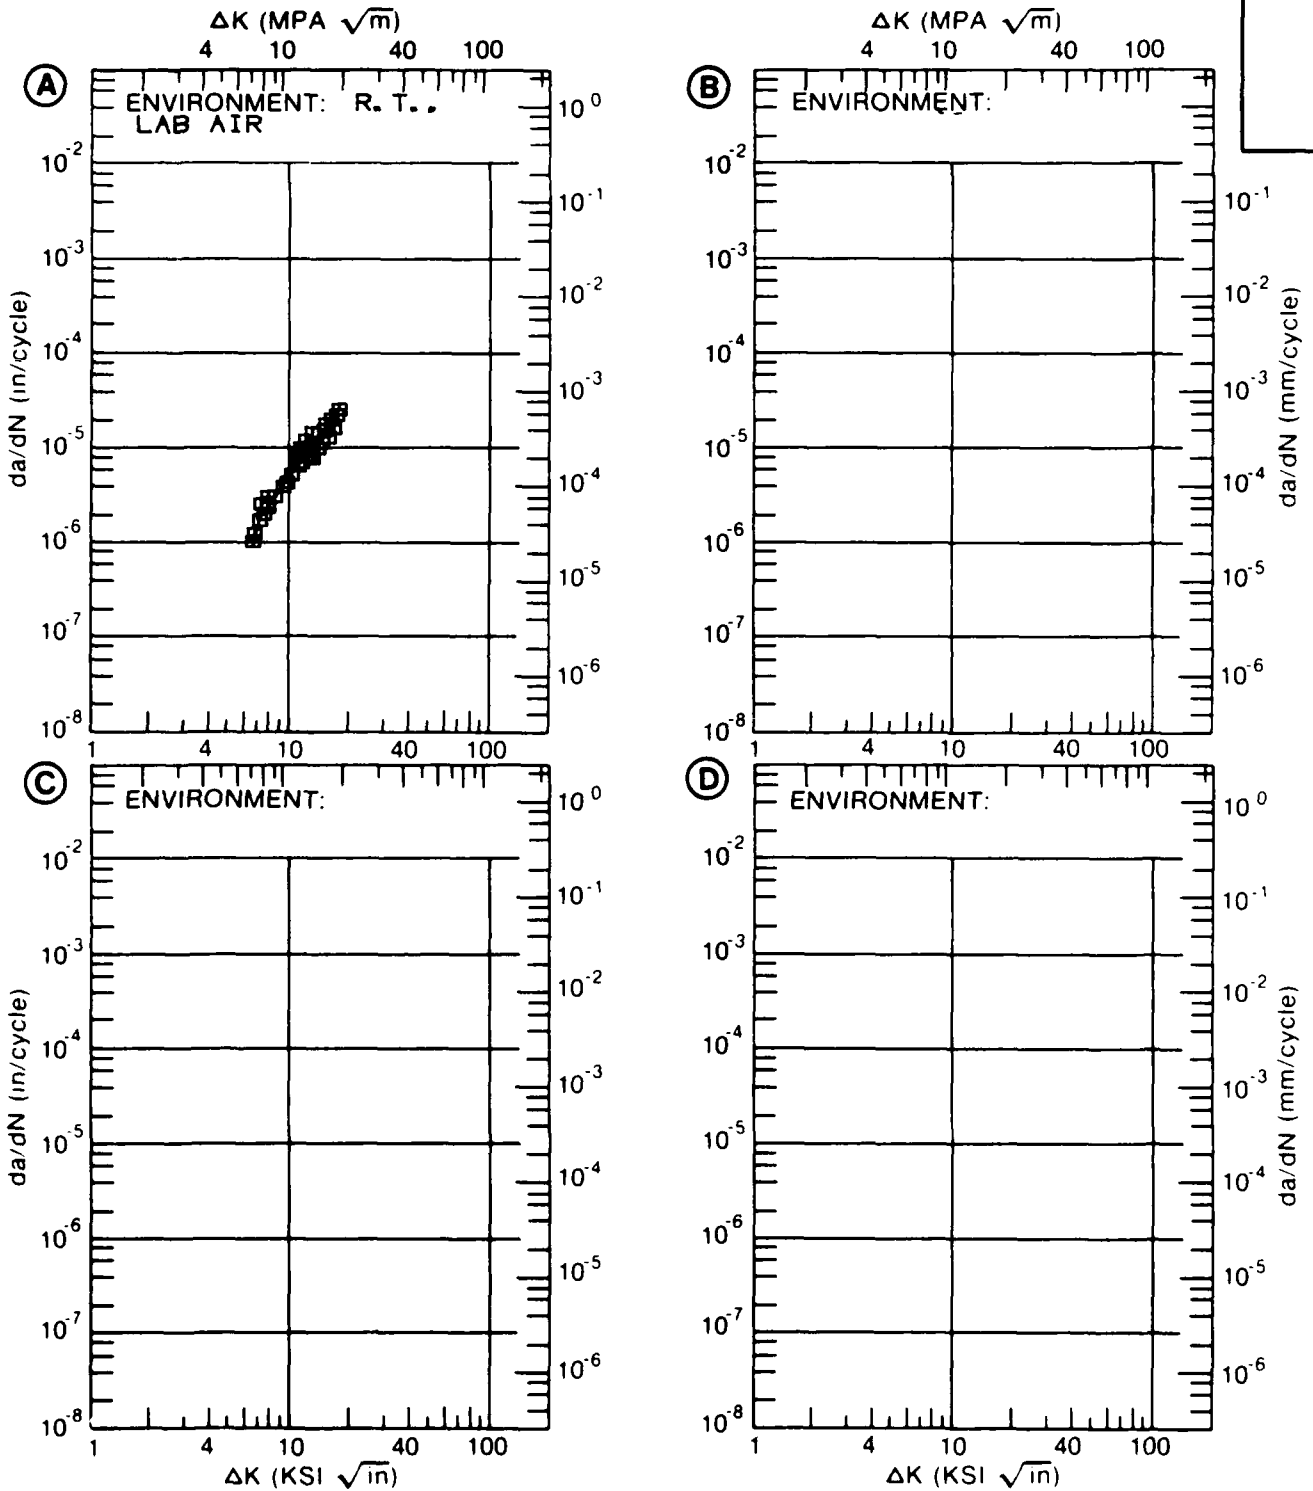


Figure 7.12.3.2

Table 7.13.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 2018 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION	PLATE	(NUMBER OF SPECIMENS)
1651	-----	I-L	-----
		S-L	14.9 ± 1.2 (12)

Table 7.13.2.1

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	THICK (IN)	SPECIMEN		K(1C)	2.5* CRACK LENGTH (IN)	K(1C)/TVS)**2	K(1C) MEAN	STAN DEV	DATE	REFER							
	FORM	THICK (IN)					WIDTH (IN)	THICK (IN)								DESIGN	A	B				
T651	P	3.34	54.8	S-L	R.T.	3.34	1.990	0.999	CT	1.014	0.21	15.90		1973	86213							
							2.000	0.999	CT	1.015	0.21	15.80		1973	86213							
							2.000	0.999	CT	1.011	0.23	16.80		1973	86213							
							2.000	0.999	CT	1.024	0.22	16.90		1973	86213							
							2.000	0.999	CT	1.034	0.16	14.10		1973	86213							
							2.000	0.999	CT	1.033	0.16	14.20		1973	86213							
							2.000	0.999	CT	1.028	0.15	13.60		1973	86213							
							2.000	0.999	CT	1.011	0.15	13.90		1973	86213							
							2.000	0.999	CT	1.018	0.14	13.20		1973	86213							
							2.000	0.999	CT	1.011	0.19	15.70		1973	86213							
							2.000	0.999	CT	1.008	0.15	14.60		1973	86213							
							2.000	0.999	CT	1.011	0.15	14.30	14.9/	1.2	1973	86213						
							T651	P	1.37	51.8	S-L	88	1.37	1.000	0.500	CT	0.499	0.47	22.90		1973	86213
														1.000	0.500	CT	0.503	0.49	23.00		1973	86213
1.000	0.500	CT	0.488	0.40	20.70	22.1/								1.2	1973	86213						

Table 7.13.2.2

CONDITION	ALUMINUM		2618		K(C)		CRACK LENGTH GROSS STRESS						K(C) STAN		K(C) STAN		
	FORM	THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	SPECIMEN		INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) STAN		K(C) MEAN (KSI*SQRT IN)	K(C) DEV (KSI*SQRT IN)	DATE	REFER	
					WIDTH (IN)	THICK B					2A(D)	2A(F)					S(D)
T61	S	0.06	R.T.	L-T	56.2	2.000	0.064	0.623	0.900	---	36.00	37.87*	49.09*	51.80*	48.23*	1973	86213
		0.06			56.2	2.000	0.064	0.623	0.970	34.10	39.70	37.55*	51.80*	48.23*	1973	86213	
		0.06			56.2	2.000	0.064	0.622	0.890	32.70	35.70	37.55*	48.23*	48.23*	1973	86213	
T61	S	0.06	R.T.	T-L	54.2	2.000	0.064	0.621	1.070	32.80	34.10	35.80*	54.12*	45.27*	1973	86213	
		0.06			54.2	2.000	0.064	0.622	0.900	---	33.20	34.92*	45.27*	45.27*	1973	86213	
		0.06			54.2	2.000	0.064	0.623	0.960	32.70	33.90	35.66*	48.76*	48.76*	1973	86213	

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.13.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.13.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2618			
CONDITION: T81					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K A:	9.66	7.21			
MIN B:					
C:					
D:					
	10.00	7.77			
	13.00	15.1			
	16.00	29.2			
DELTA K A:	16.24	30.8			
B:					
MAX C:					
D:					
ROOT MEAN SQUARE		4.38			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T81
 FORM: 0.06" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.40
 FREQUENCY: 2.00

YIELD STRENGTH: 57.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.064"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 86734

ALUM.
ALLOY

2618

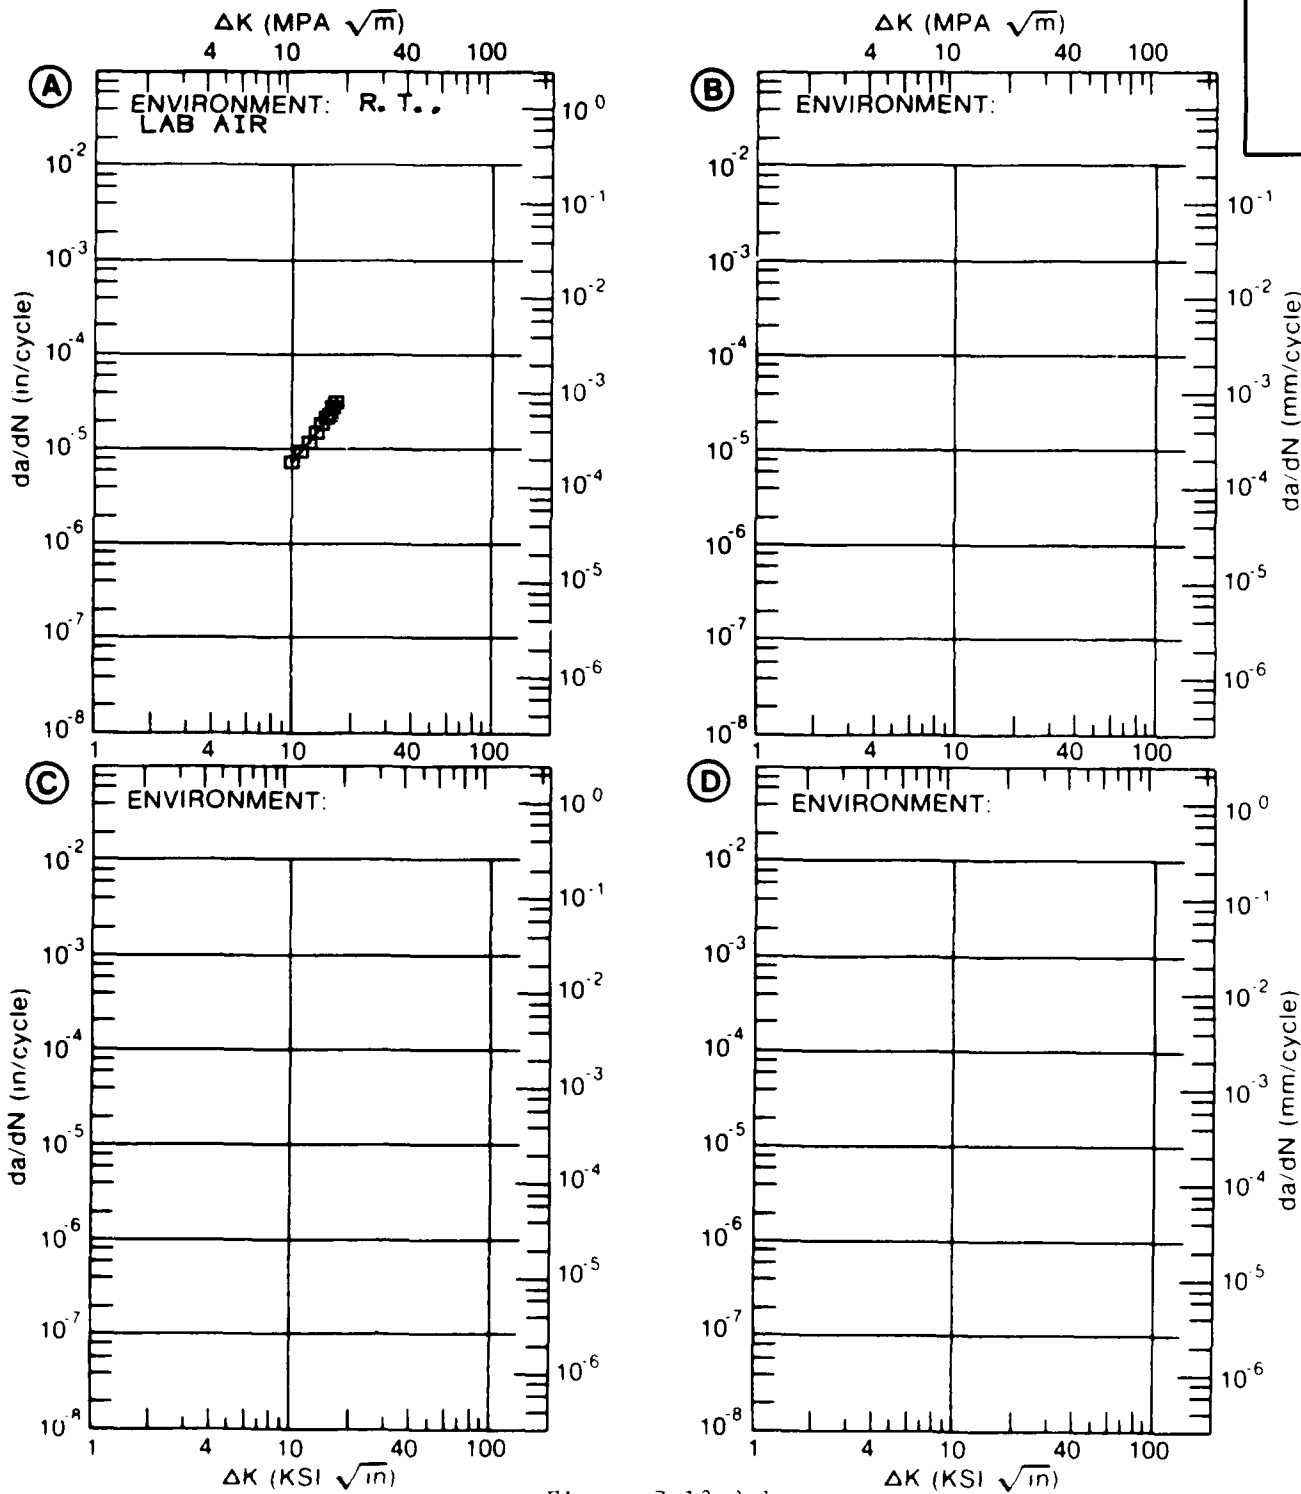


Figure 7.13.3.1

TABLE 7.13.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.13.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		2618			
CONDITION: T81					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K A:	:				
MIN B:	:				
C:	:				
D:	:				
200.00	:				
DELTA K A:	:				
MAX B:	:				
C:	:				
D:	:				
ROOT MEAN SQUARE		0.00			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T81
 FORM: 0.06" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.40
 FREQUENCY: 2.00 HZ

YIELD STRENGTH: 57.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.064"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 86734

ALUM.
ALLOY

2618

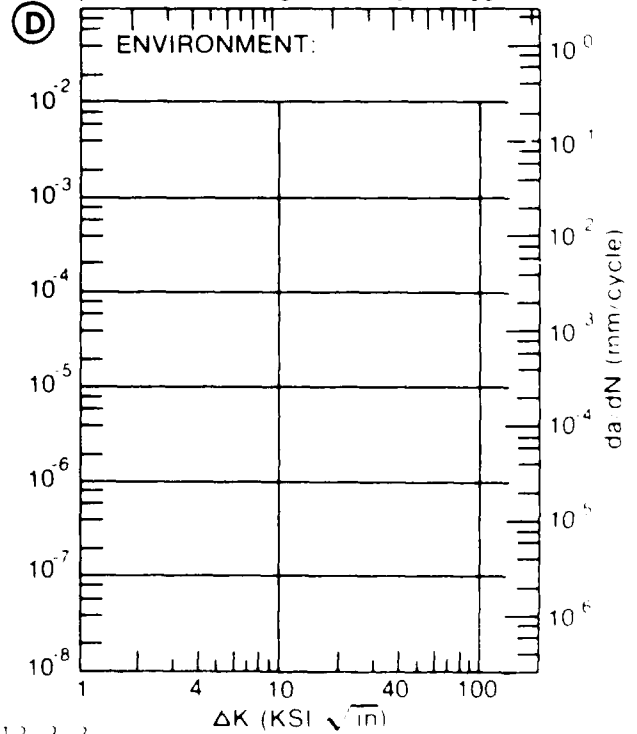
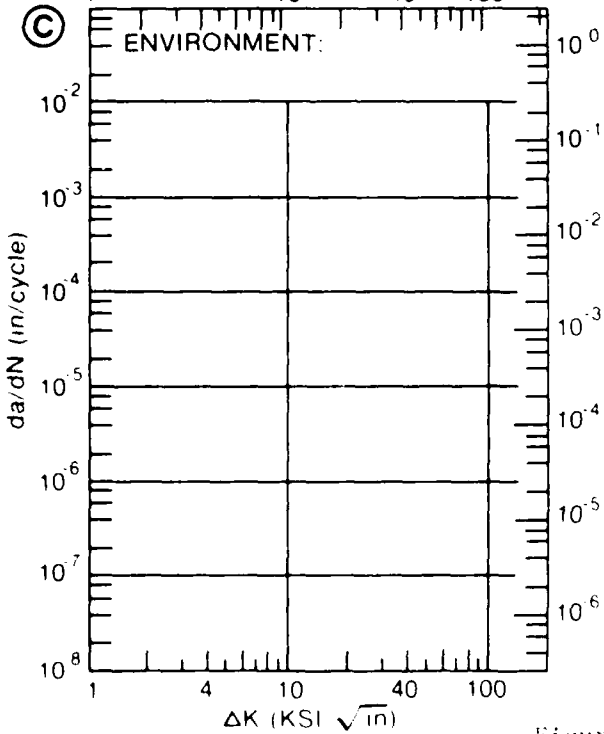
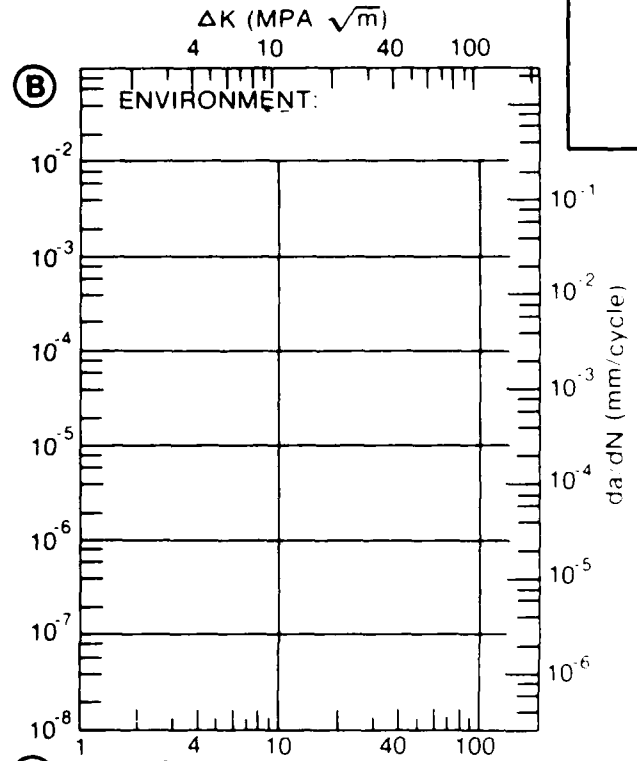
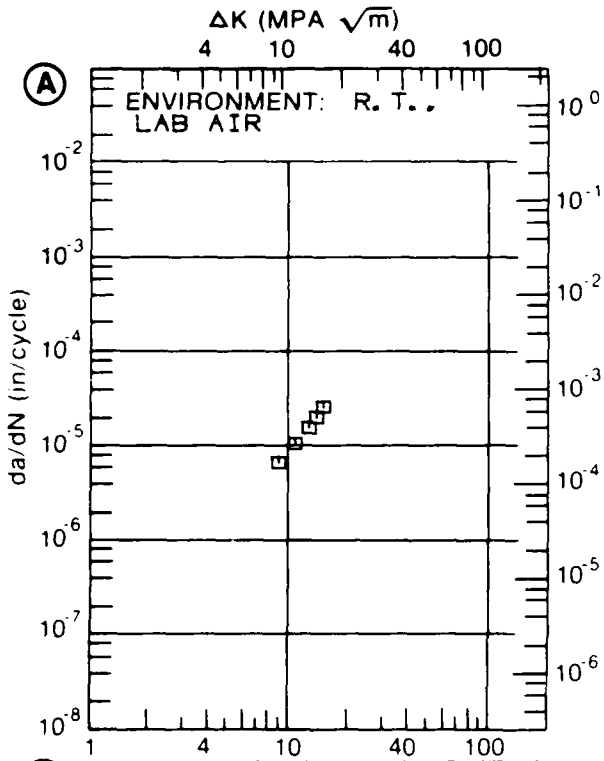


Figure 7.13.3.2

Table 7.14.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 6061 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
T651	26.6 ± 0.9	(5)
		21.5 ± 0.4 (2)

Table 7.14.2.1

CONDITION	ALUMINUM 6061 K(1C)										K(1C) STAN K(1C) MEAN DEV (KSI*SQRT IN)	DATE	REFER	
	--PRODUCT--		TEST SPECIMEN		YIELD STRENGTH		---SPECIMEN---		CRACK					2.5* (K(1C)/TYS)**2 (IN)
	FORM	THICK (IN)	THICK (F)	ORIENT	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)	A	B				
T651	P	1.50	-	112	T-L	45.5	3.000	1.480	NB	1.500	0.96	28.20	1971	84288
		1.50				45.5	3.000	1.480	NB	1.450	1.10	30.30	1971	84288
		1.50				45.5	3.000	1.480	NB	1.510	1.20	31.90	1971	84288
T651	P	1.50	R.T.		T-L	43.4	2.000	1.000	NB	1.025	0.90	26.00	1972	82880
		1.50				43.4	2.000	1.000	NB	1.018	0.94	26.60	1972	82880
		1.50				43.4	3.000	1.480	NB	1.308	1.01	27.60	1971	84288
		1.50				43.4	3.000	1.480	NB	1.443	0.86	25.40	1972	82880
		1.50				43.4	2.000	1.000	NB	0.995	0.98	27.20	1972	82880
T651	P	2.50	R.T.		S-L	41.5	2.000	1.000	CT	0.951	0.68	21.70	1973	86688
		2.50				41.5	2.000	1.000	CT	0.930	0.62	21.20	1973	86688
T651	P	3.00	88		S-L	39.6	2.490	1.251	CT	1.183	0.71	21.10	1973	86213
		3.00				39.6	2.500	1.250	CT	1.181	0.74	21.60	1973	86213
		3.00				39.6	2.500	1.250	CT	1.171	0.72	21.30	1973	86213
T651	FB	----	84		T-L	40.3	3.000	1.500	CT	1.547	1.29	28.90	1973	86213
T651	FB	----	84		S-L	40.3	2.000	1.000	CT	0.987	0.91	24.30	1973	86213
		----				40.3	2.000	1.001	CT	0.956	0.91	24.30	1973	86213
T652	F	9.00	R.T.		S-T	38.1	2.000	1.000	NB	1.000	0.95	23.40	1972	82675

Table 7.14.2.2

CONDITION	ALUMINUM		6061		K(C)		CRACK LENGTH CROSS STRESS						K(C) STAN		K(C) STAN					
	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR STR	YIELD (KSI)	---SPECIMEN---		INIT		FINAL		ONSET		MAX		K (APP) MEAN (KSI*SQRT IN)	K (C) MEAN (KSI*SQRT IN)	DEV	DATE	REFER	
					WIDTH (IN)	THICK (IN)	W	B	2A(D)	2A(F)	S(O)	S(MAX)	K (APP) MEAN (KSI*SQRT IN)	K (C) MEAN (KSI*SQRT IN)						
T6	S	0.06	R	41.9	2.000	0.062	0.622	1.240	---	28.50	29.98*	53.05*	---	---	---	---	---	---	---	---
			T	41.9	2.000	0.062	0.620	1.230	---	28.80	30.23*	53.09*	---	---	---	---	---	---	---	---
			L-T	41.9	2.000	0.062	0.619	1.360	---	28.40	29.75*	59.80*	---	---	---	---	---	---	---	---
				43.4	2.000	0.062	0.622	1.280	---	30.10	31.66*	58.31*	---	---	---	---	---	---	---	---
				43.4	2.000	0.062	0.622	1.300	---	30.00	31.56*	59.31*	---	---	---	---	---	---	---	---
T6	S	0.06	R	41.4	15.810	0.062	4.000	---	28.20	73.61*	---	---	---	---	---	---	---	---	---	---
			T	41.4	15.810	0.062	3.020	4.230	---	32.00	71.31*	86.33*	---	---	---	---	---	---	---	
			L-T	41.4	15.820	0.063	1.000	1.230	---	39.10	49.13*	54.55*	---	---	---	---	---	---	---	
				41.4	15.820	0.062	5.980	7.000	---	21.60	72.72*	81.73*	---	---	---	---	---	---	---	
				44.1	4.000	0.127	1.590	2.864	---	26.70	46.85*	86.22*	---	---	---	---	---	---	---	
T6	S	0.06	R	40.7	2.000	0.063	0.619	0.980	---	28.30	29.65*	41.43*	---	---	---	---	---	---	---	---
			T	40.7	2.000	0.062	0.623	1.280	---	28.60	30.08*	55.40*	---	---	---	---	---	---	---	
			L-L	40.7	2.000	0.063	0.620	1.110	---	28.20	29.60*	46.42*	---	---	---	---	---	---	---	
				41.8	2.000	0.062	0.622	1.130	---	29.80	31.35*	49.97*	---	---	---	---	---	---	---	
				41.8	2.000	0.062	0.617	1.320	---	29.60	30.95*	59.74*	---	---	---	---	---	---	---	
T6	S	0.06	R	40.8	15.810	0.063	3.010	4.040	---	30.10	66.95*	79.03*	---	---	---	---	---	---	---	---
			T	40.8	15.810	0.062	6.010	7.000	---	20.50	69.26*	77.98*	---	---	---	---	---	---	---	
			L-L	40.8	15.820	0.062	1.000	1.590	---	37.40	46.99*	58.71*	---	---	---	---	---	---	---	
				40.8	15.820	0.063	4.000	---	---	27.00	70.48*	---	---	---	---	---	---	---	---	
				44.1	4.000	0.503	1.600	---	---	13.40	28.90	50.94*	---	---	---	---	---	---	---	
T651	P	0.25	R	45.9	4.000	0.250	1.730	3.171	---	25.80	48.22*	101.74*	---	---	---	---	---	---	---	
T651	P	0.25	T	45.9	4.000	0.251	1.577	2.956	---	27.60	48.12*	94.20*	---	---	---	---	---	---	---	
T651	P	0.50	R	44.1	4.000	0.503	1.600	---	---	---	---	---	---	---	---	---	---	---	---	

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

Table 7.14.2.2 (Con't)

CONDITION	ALUMINUM		K(C)	CRACK LENGTH CROSS STRESS						K(C) STAN						
	---PRODUCT--- FORM THICK TEMP OR (IN) (F)	TEST SPEC YIELD STR (KSI)		---SPECIMEN--- WIDTH THICK (IN) (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	MEAN (KSI)	DEV (KSI)	STAN (IN)	MEAN (KSI)	DEV (KSI)	DATE REFER	
T651	P	0.50	R. T.	L-T	46.6	4.000	0.504	1.760	---	13.40	26.40	50.01*	---	---	1973	86213

BUCKLING OF CRACK EDGES NOT RESTRAINED

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 7.14.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 7.14.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 6061
CONDITION: T651
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	R=+0.00			
DELTA K B: MIN	A: 11.89	12.5		
	13.00	15.8		
	16.00	29.6		
	20.00	57.4		
	25.00	124.		
	30.00	259.		
	35.00	340.		
DELTA K B: MAX	A: 37.44	752.		

ROOT MEAN SQUARE 10.47
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T651
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: NB
 ORIENTATION: L-T
 FREQUENCY: 0.10 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 38.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.500"
 REFERENCES: 81507

ALUM.
ALLOY

6061

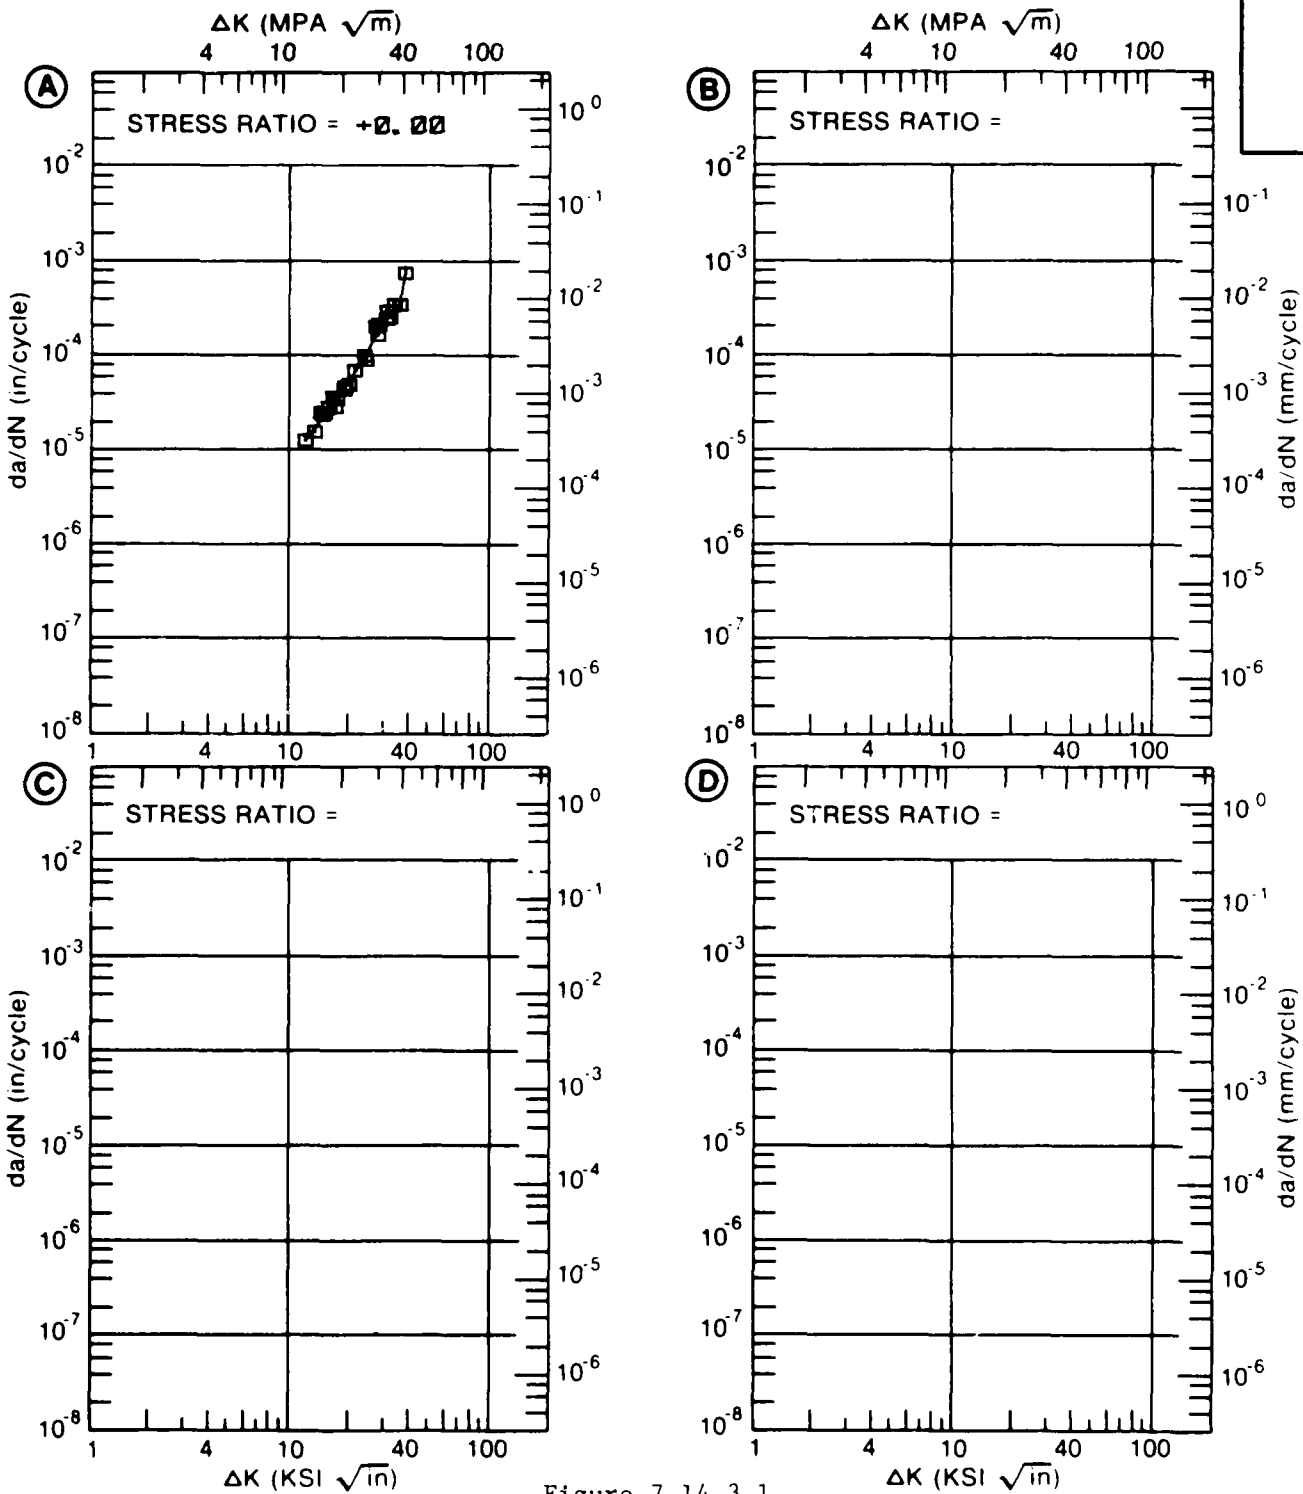


Figure 7.14.3.1

Table 7.14.3.2

CONDITION	--PRODUCT--		TEST SPEC YIELD STR (KSI)	ENVIRONMENT	ALUMINUM 6061		K (ISCC)		STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)			THICK (IN)	W	M	B			
T6	S	0.12	R. T.	S-L	AEROZINE 50	1.300	0.125	WDL	28.00*	---	1974 88700
T6	S	0.12	R. T.	S-L	AEROZINE 50/ IPCT CD2	1.300	0.125	WDL	19.60*	---	1974 88700
T6	S	0.12	R. T.	S-L	MATHESON COLE- MAN BELL 97PCT HYDROZINE /3 PCT H2O	1.300	0.125	WDL	16.40*	---	1974 88700
T6	S	0.12	R. T.	S-L	PROPELLANT GRADE HYDROZINE	1.300	0.125	WDL	25.00*	---	1974 88700
T6	S	0.12	R. T.	S-L	UNSYMMETRICAL DIMETHYL HYDROZINE	1.300	0.125	WDL	19.70*	---	1974 88700
T651	P	2.50	R. T.	S-L	41.6 INDUSTRIAL ATM	2.000	1.000	CT	21.40	20.00	1973 86688
T651	P	2.50	R. T.	S-L	41.6 SALT-DICHRO- MATE-ACETATE	2.000	1.000	CT	21.40	20.00	1973 86688
T651	P	2.50	R. T.	S-L	41.6 SEACORST ATM	2.000	1.000	CT	21.40	20.00	1973 86688
T652	F	6.00 9.00	R. T.	S-L	35.3 SEAWATER	1.400 2.000	0.700 1.000	CANT	29.60 27.40	26.00* 24.00	1972 82675 1972 82675

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

TABLE 7.15

REFERENCES FOR THE ALUMINUM ALLOY DATA

- 51527 2014-T6 K_C
Christian, J. L., and Hurlich, A., "Physical and Mechanical Properties of Pressure Vessel Materials for Application in a Cryogenic Environment", ASD-TDR-62-258, Part II, General Dynamics/Astronautics (April 1963).
- 57210 7075-T7351 K_C
Unknown
- 62306 2219-T87 K_C
7075-T6 K_C
Eichenberger, T. W., "Fracture Resistance Data Summary", Report DA-20947, The Boeing Company (June 1962).
- 62308 2024-T3 K_C
2024(ALCLAD)-T3 K_C
Anderson, W. E., "Fracture Toughness Data Summary", Report D6-9068, The Boeing Company (June 1962).
- 62309 7075-T6 K_C
Batch, E. J., and Edwards, W. T., "Evaluation of Tear Resistance of 7079 Aluminum Alloys (Sheet Extrusions and Forgings)", Report SMN 86, Lockheed Aircraft Corporation, Marietta, Ga., (April 13, 1962).
- 62310 7075-T6 K_C
7075-T651 K_C
Anon., "Fracture Toughness Data Summary of 2000 and 7000 Series Aluminum Alloys", The Boeing Company, received from J. P. Butler (April 1965).
- 62311 2024(ALCLAD)-T3 K_C
7075(ALCLAD)-T6 K_C
Gurin, P. J., "Crack Propagation Tests for Some Aluminum Alloy Materials", LR 10498, Lockheed Aircraft Corporation (February 1955).
- 65697 7075(ALCLAD)-T6 K_C
Broek, D., "The Residual Strength of Aluminum Alloy Sheet Specimens Containing Fatigue Cracks of Saw Cuts", NLR-TR M.2143, National Aerospace Laboratory, Amsterdam (March 1966).
- 66103 2219-T87 K_C
Ferguson, C. W., "Hypervelocity Impact Effects on Liquid Hydrogen Tanks", NASA CR-54852, Douglas Aircraft Company Inc. (March 1966).

TABLE 7.15 (Cont)

67821	2024-T3 K_C	Walker, E. K., "A Study of the Influence of Geometry on the Strength of Fatigue Cracked Panels", AFFDL-TR-66-92, Northrop Norair (June 196)
68908	2014-T6 K_C	Orange, T. W., "Fracture Toughness of Wide 2014-T6 Aluminum Sheet at -320 F", NASA TN D-4017, Lewis Research Center (June 1967).
69759	2219-T87 K_C	Eitman, D. A., and Rawe, R. A., "Plane Stress Cyclic Flaw Growth of 2219-T87 Aluminum and 5Al-2.5Sn ELI Titanium Alloys at Room and Cryogenic Temperatures", NASA CR-54956, Douglas Aircraft Company, Inc. (September 1966).
70485	2024(ALCLAD)-T3 K_C 7075(ALCLAD)-T6 K_C	Broek, D., "The Effect of Finite Specimen Width on the Residual Strength of Light Alloy Sheet", TR M.2152, National Aero- and Astronautical Research Institute, Amsterdam (September 1965).
70519	2024(ALCLAD)-T3 K_C	Broek, D., "The Effect of the Sheet Thickness on the Fracture Toughness of Cracked Sheet", NRL-TR M.2160, National Aerospace Laboratory, Amsterdam (January 1966).
75599	7075-T6 K_C	Hudson, C. M., "Effect of Stress Ratios on Fatigue-Crack Growth in 7075-T6 and 2024-T3 Aluminum-Alloy Specimens", NASA TN D-5390, Langley Research Center (August 1969).
75787	7075-T651 K_{Isc}	Procter, R. P. M., and Paxton, H. W., "Stress Corrosion of Aluminum Alloy 7075-T651 in Organic Liquids", Journal of Materials, <u>4</u> (3) 729-760 (September 1969).
76411	7079-T6 K_{Ic}	Wessel, E. T., et al., "Engineering Methods for the Design and Selection of Materials Against Fracture", Final Technical Report, Westinghouse Research Laboratories, Pittsburgh, PA, Contract DA-30-069-AMC-602 (T) (June 24, 1966).
77140	7075-T73510 K_{Ic} 7178-T651 K_{Ic} 7178-T6510 K_{Ic}	Kaufman, J. G., Schilling, P. E., and Nordmark, G. E., "Fracture Toughness, Fatigue and Corrosion Characteristics of X7080-T7E41 and 7178-T651 Plate and 7075-T6510, 7075-T73510, X7080-T7E42, and 7178-T6510 Extruded Shapes", Report AFML-TR-67-C-1521 (November 1969).

TABLE 7.15 (Cont)

77720	2014-T652	K_{Ic}
	2024-T852	K_{Ic} , da/dN
	7075-T7352	K_{Ic} , da/dN
	7079-T652	K_{Ic} , da/dN
	Brownhill, D. J., et al., "Mechanical Properties, Including Fracture Toughness and Fatigue, Corrosion Characteristics and Fatigue-Crack Propagation Rates of Stress-Relieved Aluminum Alloy Hand Forgings", Report AFML-TR-70-10, Aluminum Company of America, Alcoa Research Laboratory, New Kensington, PA, Contract F33615-68-C-1385 (February 1970).	
78313	2024-T351	da/dt, K_{Isc}
	2024-T4	da/dt
	2219-T37	da/dt
	7075-T651	da/dt
	7079-T651	da/dt, K_{Isc}
	7175-T66	da/dt, K_{Isc}
	Hyatt, M. V., "Use of Precracked Specimens in Stress-Corrosion Testing of High-Strength Aluminum Alloys", Summary Report D6-24466, The Boeing Company, Renton, Wash., ARPA Contract N00014-66-C-0365 (November 1969).	
78982	2024-T3	K_c
	Fedderson, C. E., Simonen, F. A., Hulbert, L. E., and Hyler, W. S., "An Experimental and Theoretical Investigation of Plane-Stress Fracture of 2024-T351 Aluminum Alloy", NASA CR-1678, Battelle Memorial Institute (September 1970).	
79089	7075-T7351	K_c
	Fedderson, C. E., and Hyler, W. S., "Fracture and Fatigue-Crack Propagation Characteristics of 7075-T7351 Aluminum Alloy Sheet and Plate Report No. G-8902, Battelle Memorial Institute, Columbus Laboratories (March 1970).	
80073	2021-T81	K_{Ic} , K_{Isc}
	7007-T6	K_{Isc}
	Schwartzberg, F. R., et al., "Cryogenic Alloy Screening", Report NASA CR-72733, Martin Marietta Corporation, Denver, CO, Contract NAS 3-11203 (November 1970).	
80104	2219-T87	K_c
	Orange, T. W., Sullivan, T. L., and Calfo, F. D., "Fracture of Thin Sections Containing Through and Part-Through Cracks", NASA TN D-6305, Lewis Research Center (April 1971).	
82675	2014-T6	K_{Isc}
	2024-T352	K_{Isc}
	2024-T852	K_{Ic} , K_{Isc}
	6061-T652	K_{Ic} , K_{Isc}
	7075-T7352	K_{Ic} , K_{Isc}
	Chu, H. P., and Wacker, G. A., "Fracture Toughness and Stress Corrosion Properties of Aluminum Alloy Hand Forgings", Journal of Materials, <u>7</u> (1) 95-99 (March 1972).	

TABLE 7.15 (Cont)

82878	2024-T351 K _{Ic}	Pearson, S., "The Effect of Mean Stress on Fatigue Crack Propagation in Half-Inch (12.7 mm) Thick Specimens of Aluminum Alloys of High and Low Fracture Toughness", Engineering Fracture Mechanics, <u>4</u> (1) 9-24 (March 1972).
82879	2014-T6 K _{Ic} 7075-T6 K _{Ic} 7075-T73 K _{Ic} 7079-T6 K _{Ic} 7080-T7 K _{Ic}	Moore, R. L., et al., "Fatigue and Fracture Characteristics of Aluminum Alloy Cylinders Under Internal Pressure", Engineering Fracture Mechanics, <u>4</u> (1) 51-63 (March 1972).
82880	2024-T851 K _{Ic} 2219-T851 K _{Ic} 6061-T651 K _{Ic} 7075-T7351 K _{Ic} 7079-T651 K _{Ic}	Nelson, F. G., et al., "The Effect of Specimen Size on the Results of Plane-Strain Fracture-Toughness Tests", Engineering Fracture Mechanics, <u>4</u> (1) 33-50 (March 1972).
83058	7175-T736 K _{Ic}	Jones, R. E., "Fracture Toughness and Fatigue Crack Growth Properties of 7175-T736 Aluminum Alloy Forging at Several Temperatures", Report AFML-TR-72-1, University of Dayton Research Institute, Dayton, OH, Contract F33615-71-C-1054 (February 1972).
83061	7049-T73 K _{Ic} , K _{Isc} 7049-T76 K _{Ic}	Jones, R. E., "Mechanical Properties of 7049-T73 and 7049-T76 Aluminum Alloy Extrusions at Several Temperatures", Report AFML-TR-72-2, University of Dayton Research Institute, Dayton, OH, Contract F33615-71-C-.054 (February 1972).
83242	7049-T73 K _{Ic} , K _{Isc} 7175-T736 K _{Ic} , K _{Isc}	Harmsworth, C. L., "Evaluation of Landing Gears Fabricated from 7175-T736 and 7049-T73 Aluminum Alloys", Report No. LA 72-22, Air Force Materials Laboratory, Wright-Patterson AFB, OH, (May 25, 1972)
83243	2024-T851 K _{Ic}	Gunderson, A. W., "Tensile, Fracture and Fatigue Properties of 2024-T851 Aluminum Thick Plate", Report No. LA 72-24, Air Force Materials Laboratory, Wright-Patterson AFB, OH, (May 26, 1972).
84284	2024-T351 da/dt 7039-T64 da/dt 7049-T73 da/dt 7075-T651 da/dt 7075-T7351 da/dt 7079-T651 da/dt 7175-T736 da/dt	Hyatt, M. V., "Use of Precracked Specimens in Stress Corrosion Testing of High Strength Aluminum Alloys", Corrosion, <u>26</u> (11), 487-503 (November 1970).

TABLE 7.15 (Cont)

84286	7075 da/dt 7075-T7351 da/dt
	Hyatt, M. V., "Use of Precracked Specimens in Selecting Heat Treatments for Stress-Corrosion Resistance in High Strength Aluminum Alloys", Corrosion, <u>27</u> (1), 49-53 (January 1971).
84288	2014-T651 K_{Ic} 2024-T851 K_{Ic} 6061-T651 K_{Ic} 7075-T651 K_{Ic} 7079-T651 K_{Ic}
	Nelson, F. G., and Kaufman, J. G., "Plane Strain Fracture Toughness of Aluminum Alloys at Room and Subzero Temperatures", ASTM STP 496, American Society for Testing and Materials, Philadelphia, PA, (1971).
84306	2024-T851 K_{Ic} 2124-T851 K_{Ic} 2219-T851 K_{Ic} 7049-T73 K_{Ic} 7075-T651 K_{Ic} 7075-T7351 K_{Ic} 7075-T7651 K_{Ic}
	Harrigan, M. J., "B-1 Fracture Mechanics Data for Air Force Handbook Usage", Report TFD-72-501, North American Rockwell, Los Angeles Division Los Angeles, CA, (April 21, 1972).
84319	2219-T87 K_{Ic}
	Engstrom, W. L., "Determination of Design Allowable Properties, Fracture of 2219-T87 Aluminum Alloy", NASA CR-115388, The Boeing Company, Aerospace Group, Seattle, Wash., Contract NAS 9-10364 (March 1972).
84329	7079-T6 K_{Isc}
	Report of NRL Progress, Naval Research Laboratory, Washington, D.C. (October 1967).
84331	2020-T651 K_{Isc} 2219-T851 K_{Isc} 7005-T63 K_{Isc} 7075-T6 K_{Isc} 7075-T651 K_{Isc} 7075-T7351 K_{Isc} 7079-T6 K_{Isc}
	Report of NRL Progress, Naval Research Laboratory, Washington, D.C. (January 1968).
84340	7075-T651 K_c 7075-T7351 K_c
	Allen, F. C., "Effect of Thickness on the Fracture Toughness of 7075 Aluminum in the T6 and T73 Conditions", ASTM STP 486, "Damage Tolerance in Aircraft Structures", p 16-38 (1971).
84360	2024-T851 da/dN, K_{Isc} 7075-T651 K_{Ic} , da/dN, K_{Isc} 7175-T736 da/dN, K_{Isc}
	McDonnell Aircraft Company, McDonnell Douglas Corporation, St. Louis, MO, Phase B Test Program, Report MDC A0913 (May 18, 1971).

TABLE 7.15 (Cont)

84362	7050-T73651 K_{Isc} 7075-T7351 K_{Isc}	
	Dill, H. D., and Rich, D. L., "Evaluation of Aluminum Plate Alloys 7075-T7351, X7050-T73651 and 2021-T81", Report No. MDC A1755, McDonnell Aircraft Company, McDonnell Douglas Corporation, St. Louis, MO, (May 30, 1972).	
84363	2021-T81 K_{Ic} 7050-T73651 K_{Ic} 7075-T7351 K_{Ic} , da/dN	
	Rich, D. L., "MCAIR IRAD Data for Fracture Mechanics Engineering and Design Data Handbook", with enclosures (1) Materials Definition, (2) Mechanical Properties Test Data, (3) Plane Strain Fracture Toughness Test Data, and (4) Plane Strain Constant Amplitude Crack Growth Test Data, McDonnell Aircraft Company, McDonnell Douglas Corporation, St. Louis, MO (June 14, 1972).	
84366	2024(ALCLAD)-T3 K_c	
	Broek, D., "Static Tests on Cracked Panels of 2024-T3 Alclad Sheet Materials From Different Manufacturers", NLR-TN M.2164, National Aerospace Laboratory, The Netherlands (November 1966).	
84367	2024-T3 K_c 7075-T6 K_c	
	McEvily, A. J., Illg, W., and Hardrath, H. F., "Static Strength of Aluminum-Alloy Specimens Containing Fatigue Cracks", NACA TN 3816, Langley Aeronautical Laboratories (October 1956).	
84368	2124-T851 K_{Ic} 7049-T73 K_{Ic} 7175-T736 K_{Ic} 7475-T61 K_c 7475-T761 K_c 7475(ALCLAD)-T61 K_c	
	Babilon, C. F., et al., "Mechanical Properties, Fracture Toughness, Fatigue, Environmental Fatigue Crack Growth Rates, and Corrosion Characteristics of High-Toughness Aluminum Alloy Forgings, Sheet and Plate", Fifth Technical Management Report, Aluminum Company of America, Alcoa Research Laboratories, New Kensington, PA, Contract F33615-71-C-1571 (August 1972).	
85291	7050-T7E56 K_{Ic}	
	Deel, O. L., and Mindlin, H., "Engineering Data on New Aerospace Structural Materials", Report AFML-TR-72-196, Volume 1, Battelle, Columbus Laboratories, Columbus, OH, Contract F33615-71-C-1262 (September 1972).	
85363	7475-T61 da/dN 7475-T6151 da/dN 7475-T7351 da/dN 7475-T761 da/dN	
	Cervay, R. R., "Engineering Design Data for Aluminum Alloy 7475 in the T761 and T61 Condition", Report AFML-TR-72-173, University of Dayton Research Institute, Dayton, OH, Contract F33615-71-C-1054, (September 1972).	

TABLE 7.15 (Cont)

85543	7075-T651		da/dt	
	7079-T651		da/dt	
	7079-T651(+50 HR at 320F)		da/dt	
	7178-T651		da/dt	
	7178-T7651		da/dt	
	Speidel, M. O., "Current Understanding of Stress Corrosion Crack Growth in Aluminum Alloys", from The Theory of Stress Corrosion Cracking in Alloys, the Proceedings of a Research Evaluation Conference, J. C. Scully (Editor), Published by NATO Scientific Affairs Division, Brussels, Belgium (1971).			
85631	2219-T87	K_{Ic}		
	2219-T87 (-300F 100HR)	K_{Ic}		
	Thatcher, C. S., "Fracture of Aluminum Alloy 2219-T87", Report SD 72-SH-0129, Space Division, North American Rockwell, Los Angeles, CA, (November 1972).			
85836	2024-T851	K_{Ic}		7075-T73651 K_{Ic}
	2024-T852	K_{Ic}		7075-T73511 K_{Ic}
	2219-T851	K_{Ic}		7075-T73652 K_{Ic}
	2219-T852	K_{Ic}		7075-T7651 K_{Ic}
	7049-T7352	K_{Ic}		
	"B-1 Fracture Toughness Data (K (sub I_c)) - Rockwell International", Rockwell International Corporation, Los Angeles, CA, (April 24, 1973).			
85837	2024-T851	da/dN		7050-T7351 da/dN
	2024-T852	da/dN		7050-T7351 da/dN
	2219-T851	da/dN		7075-T7651 da/dN
	2219-T8511	da/dN		7175-T73652 da/dN
	2219-T852	da/dN		
	"Fracture Toughness Data Collection, Rockwell International Corporation, from B-1 Program", Rockwell International Corporation, Los Angeles, CA (April 1973).			
85880	7050-T736	K_{Ic}		
	7175-T736	K_{Ic} , da/dN		
	Garland, K., "Evaluation of X7050-T736 Die Forgings", Report S14-131.10, McDonnell Aircraft Company, McDonnell Douglas Corporation, St. Louis, MO, (February 20, 1973).			
86088	7075-T6	da/dN		
	7178-T6	da/dN		
	Hudson, C. M., and Newman, J. C., Jr., "Effect of Specimen Thickness on Fatigue-Crack-Growth Behavior and Fracture Toughness of 7075-T6, and 7178-T6 Aluminum Alloys", Report NASA TN D-7173, Langley Research Center, Hampton, VA (April 1973).			
86210	2024-T852	K_{Ic}		
	7075-T73511	K_{Ic}		
	7075-T7651	K_{Ic}		
	7075-T76511	K_{Ic}		
	"Rockwell International, B-1 Fracture Toughness Data on Titanium and Aluminum Alloys of June 4, 1973", Rockwell International, Los Angeles, CA, (June 4, 1973).			

TABLE 7.15 (Cont)

86212 2024-T3 da/dN
 7050-T736 K_{Ic} , K_{Isc}
 7075-T76511 K_{Ic} , K_{Isc}
 7475-T61 da/dN
 7475-T761 da/dN, da/dt
 7475(ALCLAD)-T61 da/dN
 7475(ALCLAD)-T761 da/dN

McCarty, J. E., et al., "Materials Fracture Data From the Advanced Metallic Structures: Cargo Fuselage Design for Improved Cost, Weight and Integrity", The Boeing Company, Seattle, Washington, Contract F33615-72-C-1893 (June 15, 1973).

86213	2014-T6	K_{Ic} , K_c , da/dN	7075-T6510	K_{Ic}
	2014-T61	K_{Ic}	7075-T6511	K_{Ic}
	2014-T611	K_{Ic}	7075-T73	K_{Ic} , K_c
	2014-T651	K_{Ic} , K_c	7075-T7351	K_{Ic} , K_c
	2020-T6	K_{Ic} , K_c	7075-T73510	K_{Ic}
	2020-T651	K_{Ic} , K_c , da/dN	7075-T73511	K_{Ic}
	2020(ALCLAD)-T6	K_c	7075-T7352	K_{Ic}
	2021-T8151	K_{Ic}	7075-T76	K_{Ic} , K_c
	2024-T3	K_c , da/dN	7075-T7651	K_{Ic} , K_c
	2024-T351	K_{Ic} , K_c	7075-T7651 (SP)	K_{Ic}
	2024-T36	K_c	7075-T76511	K_{Ic}
	2024-T6	K_c	7075(ALCLAD)-T6	da/dN
	2024-T81	K_c	7075(ALCLAD)-T7651	K_{Ic}
	2024-T851	K_{Ic} , K_c	7079-T6	K_{Ic} , K_c
	2024-T852	K_{Ic}	7079-T651	K_{Ic} , K_c
	2024-T86	K_c	7079-T652	K_{Ic}
	2024(ALCLAD)-T3	K_c , da/dN	7079(ALCLAD)-T6	K_c
	2024(ALCLAD)-T86	K_c	7080-T7	K_{Ic}
	2124-T351(417)	K_{Ic}	7175-T66	K_{Ic}
	2124-T851	K_c	7175-T73	K_{Ic}
	2124-T851 (SP)	K_{Ic}	7175-T7352	K_{Ic}
	2124-T851 (417)	K_{Ic}	7175-T736	K_{Ic}
	2214-T651	K_{Ic}	7175-T73652	K_{Ic}
	2214-T651 (417)	K_{Ic}	7178-T6	K_c
	2219-T81	K_c	7178-T651	K_{Ic} , K_c
	2219-T851	K_{Ic} , K_c	7178-T7651	K_{Ic} , K_c , da,
	2219-T852	K_{Ic}	7178-T76510	K_{Ic} , da/dN
	2219-T87	K_{Ic} , K_c	7178-T76511	K_{Ic}
	2618-T61	K_c	7178(ALCLAD)-T6	K_c
	2618-T651	K_{Ic}	7178(ALCLAD)-T76	K_c
	6061-T6	K_c	7475-T6	K_{Ic}
	6061-T651	K_{Ic} , K_c	7475-T61	K_c
	7001-T75	K_{Ic} , K_c	7475-T651	K_{Ic} , da/dN
	7005-T6	K_c	7475-T651 (SP)	K_{Ic}
	7005-T6351	K_{Ic} , K_c	7475-T73	K_{Ic}
	7049-T73	K_{Ic}	7475-T7351	K_{Ic}
	7049-T7351	K_{Ic}	7475-T7351 (SP)	K_{Ic}
	7049-T7352	K_{Ic}	7475-T736	K_{Ic}
	7050-T6	da/dN	7475-T76	da/dN
	7050-T7352	K_{Ic}	7475-T761	K_c
	7050-T736	K_{Ic}	7475-T7651	K_{Ic}
	7050-T73651	K_{Ic}	7475-T7651 (SP)	K_{Ic}
	7050-T73652	K_{Ic}	7475(ALCLAD)-T73	K_c
	7050-T76	da/dN	7475(ALCLAD)-T731	K_c
	7050-T76511	K_{Ic}	7475(ALCLAD)-T761	K_c , da/dN
	7075-T6	K_c , da/dN	7475(ALCLAD)-T761	K_c , da/dN
	7075-T651	K_{Ic} , K_c		

Wygonik, R. H., "Compilation of Fracture Mechanics Data", Aluminum Company of America, Alcoa Research Laboratories, New Kensington, PA, Subcontract on F33615-73-C-5051 (June 12, 1973).

TABLE 7.15 (Cont)

86429	2024-T851 K _{Ic} 7050-T73651 K _{Ic}			
	"Fracture Toughness Data", Progress Report on Materials Test Program, General Dynamics Corporation, Fort Worth Division, Fort Worth, TX, Contract F33615-72-C-2149 (Received July 6, 1973).			
86493	7050-T73651			
	Deel, O. L., Ruff, P. E., and Mindlin, H., "Engineering Data on New Aerospace Structural Materials", Report AFML-TR-73-114, Battelle-Columbus Laboratories, Columbus, OH, Contract F33615-72-C-1280 (June 1973).			
86574	7050-T73651 K _{Ic} 7050-T7651 K _{Ic} 7475-T7651 K _{Ic}			
	Figge, F. A., and Wells, R. R., "Advanced Metallic Structure: Air Superiority Fighter-Wing Design for Improved Cost, Weight and Integrity Report No. AFFDL-TR-73-52, Volume III, Northrop Corporation, Aircraft Division, Hawthorne, CA, Contract F33615-72-C-1891 (June 1973), with original data for da/dN tests.			
86575	2024-T81 da/dN 7075-T76 da/dN			
	"Rockwell International, B-1 Program, da/dN Data, Center-Cracked Tension Specimens", Lockheed California Company, Burbank, CA, Report LR25152 (Received July 1973) (Memo from E. W. Cawthorne dated July 10, 1973).			
86688	2014-T651 K _{Isc} 2021-T81 K _{Isc} 2024-T351 K _{Isc} 2024-T851 K _{Isc} 2219-T37 K _{Isc}	2219-T87 K _{Ic} , K _{Isc} 6061-T651 K _{Ic} , K _{Isc} 7075-T651 K _{Isc} 7075-T7351 K _{Isc} 7079-T651 K _{Isc}		
	Sprowls, D. O., et al., "Evaluation of Stress-Corrosion Cracking Susceptibility Using Fracture Mechanics Techniques", Final Report, Part I, Aluminum Company of America, Alcoa Technical Center, Alcoa Center, PA, Contract NAS8-21487 (May 31, 1973).			
86734	2014-T6 da/dN 2024-T3 K _c 2024-T351 K _c 2024-T4 K _c 2024-T81 K _c , da/dN 2024(ALCLAD)-T3 K _c	2618-T81 da/dN 7075-T6 K _c 7075(ALCLAD)-T6 K _c 7079-T6 da/dN 7079-T651 da/dN		
	Smith, S. H., "Fracture Mechanics Application to Materials Evaluation and Selection for Aircraft Structure and Fracture Analysis", Report No. D6-17756, The Boeing Company, Commercial Airplane Division, Renton, Washington (July 19, 1966).			

TABLE 7.15 (Cont)

86842	<p>2124-T851 da/dN 7049-T73 da/dN 7175-T736 da/dN 7475-T61 K_{IC}, da/dN 7475-T761 K_{IC}, da/dN 7475(ALCLAD)-T61 K_{IC}</p> <p>Babilon, C. E., et al., "Mechanical Properties, Fracture Toughness, Fatigue, Environmental Fatigue Crack Growth Rates and Corrosion Characteristics of High-Toughness Aluminum Alloy Forgings, Sheet and Plate", Report AFML-TR-73-83, Alcoa Research Laboratories, New Kensington, PA, Contract F33615-71-C-1571 (April 1973).</p>
86844	<p>7050-T7351 da/dN 7050-T73651 da/dN 7050-T7651 da/dN</p> <p>"Crack Growth Rate Data Generated Under USAF Contract F33615-72-C-2165", Lockheed Aircraft Corporation, Lockheed-Georgia Company, Marietta, GA, Contract F33615-72-C-2165, Data sheets received from AFFDL August 13, 1973.</p>
87398	<p>2024-T3 da/dN</p> <p>Ellis, R., "Fracture Mechanics Studies of Fatigue Crack Propagation in 2024 Aluminum Alloy Panels Containing Transverse Slits", Report No. ARL/SM 379, Australian Defence Scientific Service, Aeronautical Research Laboratories, Melbourne, Australia, Department of Supply (August 1972).</p>
88140	<p>7075-T651 K_{IC}, da/dN 7475-T651 da/dN</p> <p>Hall, L. R., Finger, R. W., and Spurr, W. F., "Corrosion Fatigue Crack Growth in Aircraft Structural Materials", Report AFML-TR-73-204, Boeing Aerospace Company, Seattle, WA, Contract AF33615-71-C-1687 (September 1973).</p>
88174	<p>7050-T73651 K_{IC}, da/dN</p> <p>Jones, R. E., and Fudge, K. A., "Engineering Design Data for Aluminum Alloy 7050-T73651 Plate", Report AFML-TR-73-269, University of Dayton Research Institute, Dayton, OH, Contract F33615-72-C-1282 (November 1973), with supplementary data supplied by Russell R. Cervay on March 20, 1974.</p>
88186	<p>7050-T7351 K_{IC}</p> <p>"Selected Pages from Materials Section of Final Report on Cargo/Tanker Phase IA (AFFDL-TR-73-51) and Lockheed Report SMN 378", Summary Report, Lockheed-Georgia Company, Marietta, GA, Contract F33615-72-C-2165 (February 8, 1974).</p>
88468	<p>2219-T851 da/dN</p> <p>Bell, P. D., "Data Sheets for Constant Amplitude Crack Growth Data Generated by Grumman Aerospace Corporation for 2219-T851 Aluminum and Mill Annealed 6Al-4V Titanium Alloy Plate", in letter to J. E. Campbell from Grumman Aerospace Corporation, Bethpage, NJ, Contract F33615-72-C-1744 (March 15, 1974).</p>

TABLE 7.15 (Cont)

88578	2024-T861	da/dN		
	Demonet, R. J., "2024-T861 Aluminum Fracture Mechanics Test Data", Report LTR 9991-4076, Space Division, Rockwell International (January 1974).			
88579	2024-T851	da/dN	7075-T73511	da/dN
	2024-T852	da/dN	7075-T7352	da/dN
	2219-T851	da/dN	7075-T7651	da/dN
	7050-T73	da/dN	7075-T76511	da/dN
	7050-T73651	da/dN	7175-T73652	da/dN
	7075-T7351	da/dN		
	"B-1 Program da/dN Data for Aluminum Alloys", Rockwell International Corporation, memorandum to H. D. Moran from E. W. Cawthorne, Battelle's Columbus Laboratories (April 3, 1974).			
88700	6061-T6	K_{Isc}		
	Gilbreath, W. P., and Adamson, M. J., "The Stress Corrosion Susceptibility of Several Alloys in Hydrazine Fuels", NASA Technical Note, Report NASA TN D-7604, Ames Research Center, Moffett Field, CA (February 1974).			
88742	2124-T851	K_{Ic}		
	Fudge, K. A., and Jones, R. E., "Engineering Design Data for Aluminum Alloy 2124-T851 Thick Plate", Report AFML-TR-73-310, University of Dayton Research Institute, Dayton, OH, Contract F33615-72-C-1282 (January 1974).			
90011	2024-T351	K_{Ic}		
	2024-T851	K_{Ic}		
	2024-T852	K_{Ic}		
	2219-T851	K_{Ic}		
	7075-T7651	K_{Ic}		
	"Rockwell International, B-1 Program Fracture Toughness Data of August 5, 1974", with memorandum from E. W. Cawthorne to H. D. Moran of Battelle's Columbus Laboratories, (August 5, 1974).			
90981	2024-T851	K_{Ic} , da/dN		
	Krupp, W. E., Wimmer, F. T., Pettit, D. E., and Hoepfner, D. W., Data Sheets for Final Report on "Investigation of the Effects of Stress and Chemical Environments on the Prediction of Fracture in Aircraft Structural Materials", Rye Canyon Research Laboratory, Lockheed-California Company, Burbank, CA, Contract F33615-71-C-1688, data sheets received October 21, 1974.			
91123	7050-T736	K_{Ic}		
	7075-T76511	K_{Ic}		
	McCarty, J. E., et al., "Advanced Metallic Structure: Cargo Fuselage Design for Improved Cost, Weight, and Integrity", Report AFFDL-TR-73-53, Boeing Commercial Airplane Company, Seattle, WA, Contract F33615-72-C-1893 (June 1973).			
91332	7050-T736	da/dN		
	7050-T73651	da/dN		
	7050-T7651	da/dN		
	7475-T651	da/dN		
	7475-T7651	da/dN		
	Wells, R. R., "New Alloys for Advanced Metallic Fighter-Wing Structures", Northrop Corporation, Aircraft Division, Hawthorne, CA, AIAA/ASME/SAE 15th Structures, Structural Dynamics and Materials Conference, Las Vegas, NV (April 17-19, 1974)			

TABLE 7.15 (Cont)

AL001 2048-T851 K_{Ic} , da/dN
 2219-T852 K_{Ic} , da/dN
 7050-T7351 K_{Ic} , da/dN
 7475-T7351 da/dN

Brownhill, D. G., et al., "Exploratory Development for Design Data on Structural Aluminum Alloys in Representative Aircraft Environments", Alcoa Laboratories, Alcoa Center, PA, Contract No. F33615-74-C-5089, Report No. AFML-TR-77-102, July 1977.

AL002 2020-T651 da/dN
 7075-T6510 da/dN
 7075-T73510 da/dN
 7475-T651 da/dN

Data Sheets Containing Fatigue-Crack Growth Rate Data Near the Threshold on Aluminum Alloys 2020, 2024, and 7475, sent from R. J. Bucci, Aluminum Company of America, ATC, February 1982.

AL003 7475-T651 da/dN

FCGR Data Sheets for Aluminum Alloy 7475-T651 Plate, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.

AL004 7050-T76511 da/dN

FCGR Data Sheets on Aluminum Alloy 7050-T76511 and T73511, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.

AL005 7075-T651 da/dN
 7075-T6510 da/dN
 7075-T7351 da/dN
 7075-T73510 da/dN

FCGR Data Sheets on Aluminum Alloy 7075- Conditions T651, T6510, T7351, T73510, Plates, Bars, and Extrusions; Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.

AL006 7050-T73511 da/dN

FCGR Data Sheets on Aluminum Alloy 7050-T73511 Extrusions, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.

AL007 7050-T7351X da/dN

FCGR Data Sheets on Aluminum Alloy 7050-T7351X Extrusions, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.

AL008 7050-T7651X da/dN

FCGR Data Sheets on Aluminum Alloy 7050-T7651X Extrusions, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.

TABLE 7.15 (Cont)

AL009	7475-T7351 da/dN
	FCGR Data Sheets on Aluminum Alloy 7475-T7351 Plate, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.
AL010	2024-T351 da/dN
	FCGR Data Sheets on Aluminum Alloy 2024-T351 Plate, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.
AL011	2324-T39 da/dN
	FCGR Data Sheets on Aluminum Alloy 2324-T39 Plate, Received From R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.
AL012	7050(ALCLAD)-T76 da/dN
	FCGR Data Sheets on Aluminum Alloy 7050-T76 (ALCLAD), Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.
AL013	7050-T73651 da/dN
	FCGR Data Sheets on Aluminum Alloy 7050-T73651 Plate, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.
AL014	7150-T651 da/dN
	FCGR Data Sheets on Aluminum Alloy 7150-T651 Plate, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.
AL015	7050-T73651 K_{Ic} 7050-T73652 K_{Ic} , da/dN 7050-T76 da/dN
	FCGR Data Sheets on Aluminum Alloy 7050-T73651 Plate and 7050-T73652 Forging, Received from R. J. Bucci, Aluminum Company of America, Alcoa Laboratories, August 1982.
BL001	7010-T73651 K_{Ic} , K_{Iacc}
	Deel, O., "Engineering Data for New Aerospace Materials", Battelle's Columbus Laboratories, Columbus, OH, Contract No. F33615-78-C-5040, Report No. AFWAL-TR-80-4103, July 1980.
BL002	2124-T851 da/dN 7075-T7351 da/dN 7475-T7351 da/dN
	Ruff, P. E., and Smith, S. H., "Development of Mil-Hdbk-5 Design Allowable Properties and Fatigue Crack-Propagation Data for Several Aerospace Materials", Battelle's Columbus Laboratories, Columbus, OH, Contract No. F33615-75-C-5063, Report No. AFML-TR-77-162, October 1977.

TABLE 7.15 (Cont)

BW001 2014-T6 da/dN
 2024-T3511 da/dN
 7075-T6 da/dN
 7075-T6511 da/dN
 7079-T6 da/dN
 7178-T6 da/dN

Horsley, J. J., and Harris, C. E., "Durability and Damage Tolerance Assessment (DADTA) of B-52 G/H Structures, Task II, Damage Tolerance Assessment Final Report", Boeing Company, Wichita, KS, Contract No. F34601079-C-1515, Document No. D3-11560-3 June 1980.

BW002 2024-T351 da/dN
 7075-T6 da/dN
 7178-T6 da/dN

Lambert, G., Mecham, P., and Mah, T., "Durability and Damage Tolerance Assessment (DADTA) of B-52 G/H Structures, Task III, Individual Airplane Crack Growth Tracking Program", Boeing Company, Wichita, KS, Contract No. F34601-79-C-2258, Document No. D3-11560-6, November 1981.

BW005 2024-T3511 da/dN

Watson, K. R., "Weapons Bay Durability and Damage Tolerance Analysis", The Boeing Company, Wichita, KS, Contract No. F33657-78-C-0108-PZ0036, Document No. D361-40041-1, September 1980.

BW007 2024-T3511 K_{Ic}

Hananel, A., Watson, K., Knoff, K., and Sherrick, G., "Fracture Mechanics Testing of B-52/CMI Materials", Final Test Report, The Boeing Company, Wichita, KS, Contract No. F33657-78-C-0108-PZ0036, Document No. D361-11197-1, December 1978.

DA001 2024-T351 R-curve, da/dN
 7075-T6511 R-curve, da/dN
 7475-T7651 R-curve, da/dN

Fatigue Crack Growth Rate Data Sheets on Aluminum Alloys 2024, 7010, 7050, 7075 and 7475, Stainless Steel Alloys 17-4PH and 17-7PH, and Alloy Steels 4340, A286, H-11, H7-180 and 12-9-2, Sent from Paul Abelkis, Douglas Aircraft Company, McDonnell Douglas Corporation, Long Beach, CA, March 1982.

EFM01 2024-T3 da/dN
 7075(ALCLAD)-T6 da/dN

Mackay, T. L., "Fatigue Crack Propagation Rate at Low Delta K of Two Aluminum Sheet Alloys - 2024-T3 and 7075-T6", Engineering Fracture Mechanics, Volume II, p 753-761, 1979.

FRO01 2024-T3 da/dN
 2024-T351 da/dN

Fatigue Crack Growth Rate Data on 2024 Aluminum Sheet and Plate. Data sent from J. Arrighi, Fairchild Republic Company, Farmingdale, NY, March 4, 1982.

JD001 Kaarlela, W. T., and Nordquist, F. C., "Precision Aluminum Forgings Test Program for the F-16 Airplane", General Dynamics, Fort Worth Division, Report No. 16 PR678, April 1978.

TABLE 7.15 (Cont)

GD002	7175-T7354 da/dN	Kaarlela, W. T., and Nordquist, F. C., "Crack Growth Rate (da/dN) Characteristics of 7175-T7354 Bulkhead Forgings", General Dynamics, Fort Worth Division, Report No. 16 PR721, June 1977.
GD003	2124-T851 K_{Ic} , da/dN	Kaarlela, W. T., "2124-T851 Metals Allowables Testing", General Dynamics, Fort Worth Division, Report 16 PR850, October 1978.
GD004	2024-T62 da/dN 2024-T81 da/dN	Wolnaski, Z. R., "2024-T81 and -T62 0.125-Inch Sheet Metal Allowables", General Dynamics, Fort Worth Division, Report No. 16 PR853, October 1978.
GD005	2024-T62 K_C , R-curve 2024-T81 K_C , R-curve 7475-T7351 K_C , R-curve 7475-T7651 K_C , R-curve	Margolis, W. S., and Nordquist, F. C., "Plane Stress Fracture Toughness (K_C) of Aluminum Alloy 7475- One Half Inch Plate Tempers -T7651 and -T7351 and of Aluminum Alloy 2024 - One Eighth Inch Sheet -T81 and -T62 Temper", General Dynamics, Fort Worth Division, TX, Report No. 16 PR889, February 1978.
GD006	7475-T7351 K_{Ic} , da/dN, K_{Isc} 7475-T7651 da/dN, K_{Isc}	Margolis, W. S., "F-16 Material Test Allowables for Aluminum Alloy 7475, 3.0" Plate -T7351 Temper and 0.5" Plate (92" Width) -T7651 Temper and -T7351 Temper", General Dynamics, Fort Worth Division, Report No. 16 PR926, April 1978.
GD008	7075-T73 da/dN	Margolis, W. S., "F-16 Material Test Allowables of Aluminum Alloy Forgings 7075-T73 and 7049-T73", General Dynamics, Fort Worth Division, Report No. 16 PR956, July 1978.
GD011	2124-T851 K_{Ic} , K_C , R-curve 7475-T7351 K_C , R-curve	Margolis, W. S., "Plane Stress (K_C) Fracture Toughness of Thin Elements from Thick Plate of 2124-T851 and 7475-T7351 Aluminum Alloys", General Dynamics, Fort Worth Division, Report No. 16 PR1287, October 1979.
LG001	7175-T73511 K_{Ic} , K_C , K_{Isc}	Carter, F. J. et al., "C-5A Wing Modification Program - Material Characterization Program - 7175-T73511 Extrusions Final Report", Lockheed-Georgia Company, Marietta, GA, Contract No. F33657-75-C-0178, Report No. LG75ER 0186-2, September 1977.
LG002	7050(ALCLAD)-T76 K_C 7475(ALCLAD)-T61 K_C	Fuselage Materials Tests - K_C Data on Aluminum 7050-T76 and 7475-T61 Materials - sent from E. J. Batch, Lockheed Georgia Company, Marietta, GA, October 1982.

TABLE 7.15 (Cont)

LG003	7175-T73511 K_{Ic} 7175-T76511 K_{Ic}	Wygonik, R. H., "Evaluation of the R-curve for Fracture Toughness Quality Assurance Testing of Thin 7175 Aluminum Extrusions", Alcoa Laboratories, Alcoa Center, PA, for Lockheed-Georgia, Contract PO-RW18554, December 1981.
MA002	2124-T851 K_{Ic} , da/dN 7175-T73652 K_{Ic} , da/dN	Fracture Toughness of Ti-6Al-4V Plate and Forging, Aluminum 2124-T851 Plate and 7175-T73652 Forging and Fatigue Crack Growth Rate for Ti-6Al-4V Plate and Forging, Ti-6Al-6V-2Sn Extrusion, Aluminum 2124-T851 Plate and Aluminum 7175-T73652 Forging, Data submitted by D. L. Rich of McDonnell Aircraft Company, St. Louis, MO, Attachment #2, Received March 12, 1982.
MA005	7050-T7651 da/dN, K_{Isc} 7075-T7351 K_{Ic} , da/dN, K_{Isc} 7175-T73652 K_{Ic} , da/dN, K_{Isc} 7475-T7351 K_{Ic} , K_{Isc}	Garland, K., and Krieg, J. F., "Final Report - Basic Fracture Data for F-18 Materials", McDonnell Aircraft Company, St. Louis, MO, Report No. 3 NA-66-7KW, Attachment #5, March 1977.
MA006	7075-T7351 da/dN	Garland, K., and Krieg, J. F., "Evaluation of the Effect of Material Cyclic Softening and Hardening on Crack Initiation Life and Crack Growth, with and without Overloads, as a Function of Stress Ratio", McDonnell Aircraft Company, St. Louis, MO, April 1978.
MA007	7049-T7351 da/dN 7075-T6 da/dN	Garland, K., and Krieg, J. F., "Environment Load Interaction Effects on Crack Growth", McDonnell Aircraft Company, St. Louis, MO, Report No. 703-116, June 1978.
MA008	7075-T6 da/dN 7075-T651 da/dN	Garland, K., and Krieg, J. F., "Evaluation of Stress Level Effects Under Plane Stress and Plane Strain Conditions", McDonnell Aircraft Company, St. Louis, MO, Report No. TR 301-346, TM 256-5597, July 1979.
MA009	7075-T6 da/dN 7075-T651 da/dN	Garland, K., and Krieg, J. F., "Evaluation of Crack Growth Gages for Service Life Tracking Program", McDonnell Aircraft Company, St. Louis, MO, Report No. TR 703-325, TM 256-5298, December 1978.
MA011	7075-T651 K_{Ic} , da/dN 7075-T7352 K_{Ic} , da/dN 7079-T6 da/dN 7178-T651 da/dN	"Final Report, F/RF-4C/D Damage Tolerance and Life Assessment Study - Volume II", McDonnell Aircraft Company, St. Louis, MO, Contract No. AFSC F33657-73-A-0062, Report No. MDC A2883, February 197

TABLE 7.15 (Cont)

MA012 7075-T651 K_{Ic} , da/dN
 7075-T7352 K_{Ic} , da/dN
 7178-T76 da/dN

"Model F-4E Slatted Airplane Fatigue and Damage Tolerance Assessment, Volume II", McDonnell Aircraft Company, St. Louis, MO, Contract No. F33657-73-A-0004-0015, Report No. MDC A3390, July 1975.

MD001 2219-T851 K_{Ic}
 2219-T852 K_{Ic}

Davis, R. J., and Rowe, R. A., "Mechanical Properties of SRB Rolled-Ring Forgings and Large Hand Forgings", McDonnell Douglas Astronautics Company, Huntington Beach, CA, Report MDC G8545, June 1980.

MPC01	2024-T851 K_{Ic}	7075-T7651	K_{Ic}
	2024-T8510 K_{Ic}	7075(ALCLAD)-T7651	K_{Ic}
	2124-T851 K_{Ic}	7079-T651	K_{Ic}
	2219-T851 K_{Ic}	7079-T851	K_{Ic}
	2419-T851 K_{Ic}	7175-T76511	K_{Ic}
	7075-T651 K_{Ic}	7178-T7651	K_{Ic}
	7075-T6510 K_{Ic}	7475-T651	K_{Ic}
	7075-T6511 K_{Ic}	7475-T7351	K_{Ic}
	7075-T7351 K_{Ic}		

Collis, S. F., et al., "Fracture Toughness Data Bank for Aluminum Alloy Mill Products", Aluminum Company of America, Alcoa Laboratories, Alcoa Center, PA, Data Submitted by Alcoa, Reynolds Metals, Kaiser Aluminum, and Martin Marietta Aluminum and Prepared for Metal Properties Council, Inc., August 1979.

MR001 7075-T651 da/dN
 7075-T7351 K_{Ic} , da/dN
 X7090-T7E69 da/dN
 X7091-T7E70 da/dN

"Damage Tolerant Test Data on X7090, X7091, and 7075 Aluminum", Materials Research Laboratory, Inc., Glenwood, IL, Under Contract to ARRADCOM, (DAAK10-79-C-0278), Received June 1982.

NC001 7050-T736 K_{Ic}
 7050-T73651 K_{Ic}
 7149-T73511 K_{Ic}

Plane Strain Fracture Toughness Data Sets on Aluminum, Steel and Titanium Alloys, Data Sent from P. G. Porter of Northrop Corporation, March 1, 1982.

NC002 7050-T736 da/dN
 7050-T73651 da/dN
 7075-T7351 da/dN
 7149-T73511 da/dN

Fatigue Crack Growth Rate Data on Aluminum, Steel and Titanium Alloys, Data Sent From P. G. Porter of Northrop Corporation, March 1, 1982.

NC003 2024-T851 K_{Ic} , da/dN
 2124-T851 K_{Ic} , da/dN
 7050-T73651 K_{Ic}
 7075-T7351 K_{Ic} , da/dN

Chanani, G. R., et al., "Methodology for Evaluation of Fatigue Crack-Growth Resistance of Aluminum Alloys Under Spectrum Loading", Northrop Corporation, Aircraft Division, Hawthorne, CA, Contract No. N00019-80-C-0427, April 1982.

TABLE 7.15 (Cont)

RA001	2124-T851 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 36-KFP-3M04, September 1978 - June 1980.
RA002	2124-T851 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 38-KFP, November 1978.
RA003	7475-T7351 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 38KFN-7475 Alloy, March 1978 - November 1978.
RA004	7475-T7351 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 37-KFN-7475 Alloy, August 1977 - December 1977.
RA005	7475-T7351 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 38-KFN-3M04-7475 Alloy, May 1980.
RA006	7475-T7351 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 38-KFP-7475 Alloy, September 1977 - November 1977.
RA007	7475-T7651 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 37-KFP-7475 Alloy, 1977.
RA008	7050-T73651 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 37-KFP-7050 Alloy-T73651, January 1978.
RA009	7050-T73651 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 37-KFN-7050 Alloy-T73651, 1977.
RA010	7050-T73651 K_{Ic}	Summary of Plane-Strain Fracture Toughness and Notch-Tensile Tests-Reynolds Metals Company, Metallurgical Research Division, Richmond, VA, Project 38-KFP-7050 Alloy-T73651, 1977.

TABLE 7.15 (Cont)

RI002	7178-T651 da/dN				
	Data Sheets Containing Fatigue Crack Growth Rate Data on 7178-T651 Aluminum Plate Supplied by J. Stolpestad, Rockwell International, North American Aircraft Division, March 1982.				
RI003	2219-T851 da/dN				
	Chang, J. B., and Stolpestad, J. H., "Improved Methods for Predicting Spectrum Loading Effects - Phase I Report, Volume II - Test Data", Rockwell International Corporation, Los Angeles Division, Los Angeles, CA, Report AFFDL-TR-79-3036. March 1978.				
RI006	2024-T852 K _{Isc}	7075-T73 K _{Isc}			
	2124-T851 K _{Isc}	7075-T7351 K _{Isc}			
	2219-T851 K _{Isc}	7075-T73511 K _{Isc}			
	7049-T7352 K _{Isc}	7075-T7651 K _{Isc}			
	7050-T73651 K _{Isc}	7175-T73652 K _{Isc}			
	Ferguson, R. R., and Berryman, R. C., "Fracture Mechanics Evaluation of B-1 Materials", Rockwell International, B-1 Division, Los Angeles, CA, Contract No. F33657-70-C-0800, Report No. AFML-TR-76-137, October 1976.				
UD002	7010-T73651 da/dN				
	Cervay, R. R., "An Empirical Model for Loading Ratio Effect on Fatigue Crack Growth Rate Data", University of Dayton Research Institute, Dayton, OH, Contract No. F33615-80-C-5011, Report No. AFWAL-TR-81-4140, November 1981.				
UD003	7010-T73651 K _{IC} , da/dN, K _{Isc}				
	Cervay, R. R., "Mechanical Property Evaluation of Aluminum Alloy 7010-T73651", University of Dayton Research Institute, Dayton, OH, Contract No. F33615-78-C-5002, Report No. AFWAL-TR-80-4094, July 1980.				
UD004	2419-T851 K _{IC} , da/dN				
	Ruschau, J. J., "Mechanical Property Data for Aluminum Alloy 2419-T851 Plate", University of Dayton Research Institute, Dayton, OH, Contract No. F33615-74-C-5024, Report No. AFML-TR-75-136, September 1975.				
UD005	2124-T851 K _{IC} , da/dN				
	Ruschau, J. J., "Complete Fatigue Crack Growth Rate Curves for Aluminum Alloy 2124-T851 Including Typical Crack Growth Models", University of Dayton Research Institute, Dayton, OH, Contract No. F33615-78-C-5002, Report No. AFML-TR-78-155, November 1978.				
UD006	2024-T3 da/dN				
	7075-T73 da/dN				
	Ruschau, J. J., "The Effect of Negative R-Ratio on Fatigue Crack Growth Rate Properties for Aluminum 7075-T73 and 2024-T3", University of Dayton Research Institute, Dayton, OH, Contract No. F33615-78-C-5002, Technical Memorandum UDR-TM-80-07, March 1980.				

TABLE 7.15 (Cont)

UD009	2024-T351 da/dN
	Cervay, R. R., "An Empirical Model for Load Ratio and Test Temperature Effects on the Fatigue Crack Growth Rate of Aluminum Alloy 2024-T351", University of Dayton Research Institute, Dayton, OH, Contract No. F33615-80-C-5011, Report No. AFWAL-TR-82-4025, March 1982.
UD010	2219-T851 da/dN
	Miller, M. S., and Gallagher, J. P., "An Analysis of Several Fatigue Crack Growth Rate (FCGR) Descriptions", University of Dayton Research Institute, Dayton, OH.
WA001	7049-T73511 K_{Ic}
	7050-T73511 K_{Ic} , da/dN
	7075-T73511 K_{Ic} , da/dN
	Petrak, G. J., "Effects of Purity Level on the Mechanical Properties of 7000-Series Aluminum", Air Force Wright Aeronautical Laboratories (AFWAL/MLSA), Air Force Systems Command, WPAFB, OH, Project No. 2418, April 1980.

CHAPTER 8

7000 SERIES ALUMINUM ALLOY SECTIONS

8.0	7000 Series Aluminum Material Summaries
8.1	7001
8.2	7005
8.3	7007
8.4	7010
8.5	7039
8.6	7049
8.7	7050
8.8	7050 (Alclad)

TABLE 8.0.1

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	KC	R	CURVES	EA/DN	DA/DI	MISCC
7001	T75	PLATE SHEET	X	X	X			X		
7005	T6	SHEET PLATE		X	X			X		
	T63	PLATE								X
	T6351	PLATE	X	X						
7007	T6 OVERHEATED WELD CENTER LINE	PLATE								X
	T6 REPAIRED WELD FUSION LINE	PLATE								X
	T6 REPAIRED WELD HEAT AFFECT ZONE	PLATE								X
	T6 REPAIRED WELD CENTER LINE	PLATE								X
	T6 WELD CENTERLINE	PLATE								X
7010	T6 WELD FUSION LINE	PLATE								X
	T6 WELD HEAT AFFECT ZONE	PLATE								X
	T6 WELD CENTERLINE	PLATE	X	X				X		X
7039	T64	PLATE						X		
7049	T77	FORGING	X	X				X		X
		EXTRUSION	X	X				X		X
		EXTRUDED BAR	X							X
7735	T73 INTEGRALLY STIFFENED	EXTRUSION								X
	T7351	PLATE	X					X		

TABLE 8.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	KC	R CURVES	TA/DN	DA/DT	K1SCC
7049	T73511-HIGH PURITY	EXTRUSION EXTRUDED BAR	X				X		
		EXTRUSION EXTRUDED BAR	X						
	T73511 LOW PURITY	EXTRUSION EXTRUDED BAR	X						
		EXTRUSION EXTRUDED BAR	X						
	T73511 MEDIUM PURITY	FORGING	X						X
		EXTRUDED BAR	X						
7050	T6	SHEET EXTRUSION					X		X
		FORGING					X		X
	T7F54	FORGING	X						
		FORGING						X	
	T7351	PLATE	X					X	
		EXTRUSION						X	
	T7351X	EXTRUSION						X	
		EXTRUSION EXTRUDED BAR	X						
	T73511-HIGH PURITY	FORGING	X						
		FORGING	X					X	
PLATE EXTRUSION		X					X	X	
FORGING		X						X	

TABLE 8.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/TUT	PRODUCT FORM	K1C	K1C	R CURVES	DA/DN	DA/DT	K1SCC	
7050	176	SHEET				X			
	T7451	PLATE	X			X		X	
	T7651X	EXTRUSION				X			
	T74511	EXTRUSION PLATE	X			X	X		
7050 (ALCLAD)	176	SHEET		X		X			
		PLATE					X		
7075	16	FORGING	X	X					
		EXTRUSION	X	X					
		FORGED BAR	X						
		ROLLED BAR	X						
		SHEET		X			X		X
	PLATE		X			X			
	1651	PLATE		X				X	
		EXTRUSION		X				X	
		ROLLED BAR		X					X
		SHEET			X				
-----							X		
16510	EXTRUSION		X				X		
	FORGED BAR		X				X		
	EXTRUDED BAR								
16511	EXTRUSION		X				X		
	FORGING		X					X	
173	FORGED BAR		X				X		
	SHEET			X					
	PLATE					X			
T7351	PLATE		X				X		
	EXTRUSION SHEET		X				X		
T73510	EXTRUSION		X				X		
	EXTRUDED BAR						X	X	

TABLE 8.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/TIT	PRODUCT FORM	KIC	KC	R CURVES	DA/DN	DA/DT	KISCC
7075	T73511	EXTRUSION EXTRUDED BAR	X			X		X
		EXTRUSION EXTRUDED BAR	X			X		
		EXTRUSION EXTRUDED BAR	X			X		
		EXTRUSION EXTRUDED BAR	X			X		
7075 (AI (1AP))	T6	SHEET		X				
		PLATE	X	X				X
		PLATE	X					
7075	T6	PLATE	X					
		EXTRUSION	X			X		X
		PLATE					X	
7075	T6	PLATE	X					
		FORGING	X			X		X
		EXTRUSION	X			X		X
		BILLET	X			X		X
7075	T6	PLATE	X					
		EXTRUSION	X			X		X
		EXTRUSION	X			X		X
		PLATE					X	
7075	T6	PLATE	X					
		FORGING	X			X		X
		EXTRUSION	X			X		X
		BILLET	X			X		X
7075	T6	PLATE	X					
		FORGING	X			X		X
		EXTRUSION	X			X		X
		BILLET	X			X		X

TABLE 8.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	R	CURVES	DA/DN	DA/DT	KISCC
7079	T651	PLATE SHEET	X	X	X		X	X	X
	1651+50HR AT 370F	PLATE					X		
	1651+500HR AT 370F	PLATE					X		
	1651	FORGING	X			X			
	1651	PLATE	X						
	T6	SHEET		X					
7080	T7	FORGING FORCED BAR	X	X					
7090	T7E69	PLATE				X			
7091	T7E70	PLATE				X			
7149	T73511	EXTRUSION	X			X			
7150	1651	PLATE				X			
7175	166	FORGING	X				X		X
	173	FORGING	X						
		EXTRUSION	X						
	T73511	EXTRUSION	X	X					X
	T7352	FORGING	X						
	T7374	FORGING					X		

TABLE 8.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION/HT	PRODUCT FORM	K1C	KIC	R CURVES	DA/DN	DA/DT	KISCC
7175	1736	FORGING	X			X		X
	1736/57	FORGING	X			X		X
	176511	EXTRUSION	X					
7178	16	SHEET		X		X		
	1651	PLATE EXTRUSION SHEET	X	X		X		X
	16510	EXTRUSION	X			X		
	1651+1HR AT 160F	PLATE					X	
	1651+1HR AT 300F	PLATE					X	
7179	1651+1HR AT 500F	PLATE					X	
	176	SHEET				X		
	17651	PLATE	X	X		X		X
	176510	EXTRUSION FORGED BAR EXTRUDED BAR	X	X		X		X
	176511	EXTRUSION	X					
7190	176	SHEET					X	
	176	SHEET					X	

TABLE 8.0.1 (con't)

AVAILABLE DATA FOR ALUMINUM ALLOYS

ALLOY	CONDITION	PRODUCT FORM	K1C	KIC	R CURVES	DA/DN	DA/DT	KISCC
7475	T6	PLATE	X					
	T61	SHEET		X				X
		PLATE		X				X
	T6151	SHEET				X		X
		PLATE	X			X		X
	T651 (SP)	PLATE	X					
		PLATE	X					
	T73	PLATE	X					
	T7351	PLATE	X	X	X			X
		PLATE	X					
T7351 (SP)	PLATE	X						
	FORGING	X						
T746	SHEET				X		X	
	SHEET PLATE		X	X			X	
T7651	PLATE	X	X	X			X	
	SHEET							
T7651 (SP)	PLATE	X						
	SHEET							
7475 (AL CLAD)	T61	SHEET		X			X	
		PLATE		X			X	
7475	T73	SHEET		X			X	
		PLATE		X			X	
7475	T731	SHEET		X			X	
		PLATE		X			X	
7475	T761	SHEET		X			X	
		PLATE		X			X	

TABLE 8.0.2

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K1C (KSI SQRT(IN))							
				L-T			S-L				
				SPECIMEN THICK *	MEAN	STD DEV	SPECIMEN THICK *	MEAN	STD DEV		
7001	T75	PLATE	1 37	1 36	24 1	1 7	1 36	20 7	1 8	---	---
7005	T6351	PLATE	3 00	2 95	46 7	1 0	2 96	39 7	0 9	---	---
7010	T73651	PLATE	2 00	0 75	33 5	4 6	0 75	27 9	2 6	0 75	23 1 0 5
7049	T73	FORGING	1 00-7 10	0 50	30 8	3 0	1 00	21 9	2 5	0 50	21 3 2 5
	T73	EXTRUSION	3 00	1 00	28 1	0 7	1 00	25 2	0 5	---	---
		EXTRUDED BAR	3 25-3 50	1 00	33 2	2 7	1 00	22 0	0 5	---	---
	T7351	PLATE	2 00-4 00	---	---	---	0 75	26 1	1 7	0 75	23 8 0 6
	T73511 HIGH/ PURITY	EXTRUDED BAR	1 50	1 25	33 9	0 1	1 25	26 0	0 1	---	---
	T73511-LOW/ PURITY	EXTRUDED BAR	1 50	1 25	23 8	0 3	1 25	18 1	0 1	---	---
	T73511 MEDIUM/ PURITY	EXTRUDED BAR	1 50	1 25	29 7	0 8	1 25	22 1	0 5	---	---
	T7352	FORGING	3 00-7 10	2 00	38 2	1 0	---	---	---	1 00	19 5 2 8
	T76	EXTRUDED BAR	3 25-3 50	1 00	32 7	1 7	1 00	20 0	0 3	---	---
7050	T7E56	FORGING	5 00	---	---	---	0 75	28 9	3 9	---	---
	T7351	PLATE	1 00-6 00	1 00	34 8	3 9	1 50	30 0	2 6	0 75	28 0 1 3
	T73511-HIGH/ PURITY	EXTRUDED BAR	1 50	1 25	36 2	3 2	1 25	24 1	0 2	---	---
	T776	FORGING	3 00-6 00	0 70	32 3	2 3	1 00	23 4	1 0	1 51	24 6 0 6
	T73651	PLATE	1 00-6 00	0 98	31 9	3 9	0 99	28 7	4 7	0 97	23 5 1 5

* MINIMUM SPECIMEN THICKNESS (IN)

TABLE 8.0.2 (con't)

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ HT	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K _{IC} (KSI SQRT(IN))			5 L					
				MEAN	STD DEV	SPECIMEN THICK *	MEAN	STD DEV	SPECIMEN THICK *			
7050	17-65F	FORGING	3.50-7.50	1.50	2.5	1.50	20.7	1.4	0.75	19.2	1.4	
	17-651	PLATE	1.00	1.00	30.8	0.3						
7075	76	FORGING	0.50-0.89	0.50	24.3	0.1	0.29	20.9	1.7	0.50	16.8	0.4
		EXTRUSION	2.00				0.75	19.9	0.2	0.75	18.5	0.2
	1-51	PLATE	0.37-5.00	0.51	26.5	2.0	0.30	27.5	2.0	0.50	17.6	2.7
70510		EXTRUSION	3.00-5.00	1.50	31.1	0.5	1.50	20.2	0.2			
		ROLLED BAR	5.00	1.50	34.1	0.5						
	13-510	EXTRUSION	0.68-3.50	0.50	27.5	2.1	0.50	23.3	1.6	0.25	20.0	1.3
		FORGED BAR	0.68-5.00	0.62	29.2	3.4	0.50	21.4	1.8	0.25	18.7	0.9
70511		EXTRUSION	1.25	1.22	27.9	1.4	1.17	26.9	1.8			
	1-3	FORGING	1.00							0.50	19.1	0.5
7051		PLATE	1.00-4.00	0.51	29.4	2.2	0.51	26.2	3.2	0.50	18.5	0.4
	17-6510	EXTRUSION	0.68-3.50				0.50	24.6	2.3	1.00	20.3	0.8
70511		EXTRUSION	3.50	1.63	39.6	3.1	1.75	26.8	1.1	1.00	21.9	1.1
	17-6511 HIGH/ PURITY	EXTRUDED BAR	1.50	1.25	43.0	1.7	1.25	30.0	0.1			
70511 LOW/ PURITY		EXTRUDED BAR	1.50	1.25	27.3	0.2	1.25	21.7	1.7			
	17-6511 MEDIUM/ PURITY	EXTRUDED BAR	1.50	1.25	30.6	0.2	1.25	21.9	0.3			
7052		FORGING	2.00-6.00	0.75	33.6	3.1	0.75	26.6	2.8	0.50	21.7	3.2
	17-652	FORGING	6.00	2.00	35.0	1.8	1.75	26.6	2.7			

* MINIMUM SPECIMEN THICKNESS (IN)

TABLE 8.0.2 (con't)

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/ -T	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K1C (KSI SQRT(IN))		L-T		T-L		S-L				
				MEAN	STD DEV	SPECIMEN THICK *	MEAN	STD DEV	SPECIMEN THICK *	MEAN	STD DEV	SPECIMEN THICK *	MEAN	STD DEV
7075	T7651	PLATE	0.56-2.60	0.75	28.5	1.5	0.50	23.1	2.0	0.38	17.8	1.5		
	T76511	EXTRUSION	1.44-7.04	1.17	35.7	4.4	1.25	23.6	2.8					
7075 (ALCLAD)	T7651	PLATE	0.50-0.62	0.62	28.6	2.2	0.50	25.2	1.9					
	T6	PLATE	3.00	1.00	33.0	2.9								
	T651	PLATE	1.00-5.00	0.97	27.6	1.8	0.50	23.3	2.0	0.50	18.6	3.2		
	T652	FORGING	2.00-6.00	0.75	27.8	2.2	0.75	23.1	2.2	0.25	18.1	0.7		
7149	T651	PLATE	1.37-1.50	1.00	28.6	1.6	1.00	21.3	3.4					
	T76511	EXTRUSION	3.00	1.01	31.5	0.8	1.01	24.2	0.3					
7175	T66	FORGING	1.00				0.50	23.2	3.1	0.50	20.8	1.1		
	T76511	EXTRUSION	1.00-8.50							0.50	27.1	1.2		
7175	T7652	FORGING	0.75				0.50	27.0	4.9					
	T736	FORGING	1.00-4.00				0.62	24.5	0.5					
	T73652	FORGING	1.25-3.10	0.50	31.2	3.8	0.90	26.4	3.6	0.50	25.3	2.1		
	T76511	EXTRUSION	1.40-3.75	0.60	32.9	3.5	0.60	22.6	2.5	0.75	20.9	1.3		
7175	T651	PLATE	0.50-1.37	0.50	25.3	1.9	0.46	21.5	1.8	0.50	15.0	0.3		
	T6510	EXTRUSION	0.68-3.50				0.50	18.5	1.3	1.00	14.5	0.1		
7175	T7651	PLATE	0.50-2.00	0.45	27.8	1.8	0.45	23.1	2.4	0.50	17.3	0.4		
	T76510	EXTRUSION	0.68-3.50	0.62	30.5	0.9	0.62	26.8	1.1	1.00	16.2	0.4		
		FORGED BAR	3.50				0.50	19.2	1.2					

TABLE 8.0.2 (con't)

PLANE STRAIN FRACTURE TOUGHNESS VALUES OF ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	(CONDITION/ HT)	PRODUCT FORM	RANGE OF PRODUCT THICKNESSES (IN)	K1C (KSI SQRT(IN))			T-L			S-L				
				SPECIMEN THICK *	MEAN	STD DEV	SPECIMEN THICK *	MEAN	STD DEV	SPECIMEN THICK *	MEAN	STD DEV		
717A	T74511	EXTRUSION	0.40-1.44	0.40	25.7	0.3	---	---	---	---	---	---	---	---
7475	T651	PLATE	0.62-2.62	0.86	40.1	2.4	0.65	34.6	3.5	1.00	32.9	2.5	---	---
	T651 (SP)	PLATE	1.30-2.00	1.28	35.3	1.9	1.28	34.4	2.1	0.50	27.3	1.6	---	---
	T7751	PLATE	1.25-4.00	1.27	47.1	4.9	1.00	37.1	4.0	0.50	30.6	2.6	---	---
7751 (SP)	T7751	PLATE	1.75-3.25	---	---	---	0.75	37.6	2.5	---	---	---	---	---
	T7451	PLATE	0.87-2.00	0.95	40.4	2.3	0.89	34.0	2.9	0.75	27.6	0.8	---	---
	T7651 (SP)	PLATE	1.75-2.00	1.79	42.4	2.9	1.00	35.7	0.4	0.75	27.3	2.1	---	---

* MINIMUM SPECIMEN THICKNESS (IN)

TABLE 8.0.3.1

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS OF
7000 SERIES ALUMINUM ALLOYS (WITH BUCKLING CONSTRAINTS)

ALLOY	CONDITION/HT	TEST TEMP. (°F)	SPECIMEN ORIENT	SPECIMEN WIDTH	YIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN.) = 0.010	0.050-	0.080	0.100-	0.120	0.250
7050 (Alclad)	T76	R. T.	L-T	20.0	67.2	114.1/7.6(2)					
7075	T6	R. T.	L-T	12.0	75.9				71.9/2.8(26)		
				24.0	75.9				71.5/0.2(2)		
				36.0	75.9				72.8/6.1(5)		
	1651 1721	R. T.	T-L	15.0	76.2						
		R. T.	L-T	24.0	75.5				73.4/8.2(10)		76.6/0.3(2)
		R. T.	L-T	8.0	78.3				63.4/5.5(6)		
7075 (Alclad)	T6	R. T.	L-T	60.5						119.9/24.0(2)	
7475 (Alclad)	T61	R. T.	L-T	15.0	67.4	8.8/4.1(2)					
				6.0	73.1				60.1/5.1(6)		
				12.0	73.1				70.1/7.2(17)		
				24.0	73.1			69.3/10.4(20)			
				20.0	69.4						129.8/3.0(2)

Mean/Standard Deviation (Number of Specimens)

TABLE 8.0.3.3.2

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS
OF 7000 SERIES ALUMINUM ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

ALLOY	CONDITION/ HT	TEST TEMP (°F)	SPECIMEN ORIENT	WIDTH (IN)	FIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	$K_{IC} \text{ (Ksi}\sqrt{\text{in}})$													
							0.010	0.020	0.030	0.040	0.063	0.080-0.090	0.125	0.160	0.180	0.250	0.500	1.000		
7050	T75	R.T.	L-T	20.0	-71													33.1/ 6.0(12)		
			T-L	3.0	68.0														39.5/ 2.7(12)	
				20.0	70.6														28.7/3.3(12)	
	T6	R.T.	L-T	15.8	-77														60.2/ 1.4(3)	
			T-L	4.5	75.5														58.3/ 4.0(2)	
				15.8	72.9															62.2/ 3.4(5)
				24.0	-72															46.3/ 5.9(7)
T651	R.T.	L-T	3.0	-73														51.5/ 2.5(8)		
			4.0	74.1														54.3/ 4.9(2)		
			15.0	-75															37.8/ 1.6(2)	
			3.0	-78															57.5/ 3.8(2)	
			4.0	-78															46.3 0.0(2)	
	20.0	-78															61.3/ 4.7(2)			

Mean/Standard Deviation (Number of Specimens)

TABLE 8.0.3.2 (con't)

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS
OF 7000 SERIES ALUMINUM ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

ALLOY	CONDITION/ HT	TEST TEMP (°F)	SPECIMEN ORIENT WIDTH	FIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	K _c (Ksi√in)									
						0.010	0.020	0.030	0.040	0.063	0.080-0.090	0.125	0.160	0.180	0.250
7051	T651	R.T.	T-L	3.0	±75										
7051	T73	88	L-T	16.0	60.0										
7051	T7351	R.T.	L-T	8.0	62.1										
7051	T651	R.T.	T-L	16.0	61.1										
7051	T651	R.T.	L-T	15.0	±70										
7051	T651	R.T.	L-T	9.0	63.0										
7051	T651	R.T.	L-T	20.0	63.0										
7051	T651	R.T.	L-T	30.0	71.8										

TABLE 8.0.3.2 (con't)

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS
OF 7000 SERIES ALUMINUM ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

ALLOY	CONDITION/ HT	TEST TEMP (°F)	SPECIMEN ORIENT	WIDTH (IN)	FIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	K _c (Ksi/in)																
							= 0.010 0.020 0.030 0.040 0.063 0.080-0.090 0.125 0.160 0.180 0.250 0.500 1.000																
7075 (Al. Last)	T ₆	R.T.	T-L	15.0	≥66	65.1/ 0.4(2)	78.4/ 2.6(2)	90.5/ 0.0(2)	0.030	0.040	0.063	0.080-0.090	0.125	0.160	0.180	0.250	0.500	1.000					
																			75.5/ 0.4(2)	52.0/ 1.0(2)			
	T ₆	84	T-L	16.0	69.1	67.8/ 1.5(2)	49.7/ 0.6(2)	51.6/ 1.8(3)	64.9/7.6(12)	51.7/ 0.6(3)	40.5/ 2.6(2)	38.8/ 3.8(13)											
													46.3/ 3.3(11)	47.8/ 2.2(5)	50.4/ 5.0(14)								
7075	T ₆	R.T.	L-T	3.0	74.7	20.0	3.0	≥72	20.0	2.0	≥82	3.0	≥83	15.0	2.0	≥80	3.0	≥78	15.0	≥78			
																					46.3/ 3.3(11)	47.8/ 2.2(5)	50.4/ 5.0(14)
																					46.5/ 1.8(5)		

Mean/Standard Deviations (Number of Specimens)

TABLE 8.0.3.2 (con't)

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS
OF 7000 SERIES ALUMINUM ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

ALLOY	CONDITION/ HT	TEST TEMP (°F)	SPECIMEN ORIENT WIDTH	FIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	K_{IC} (KSI \sqrt{IN})	0.010	0.020	0.030	0.040	0.063	0.080-0.090	0.125	0.160	0.180	0.250	0.500	1.000
7178	T651	R.T.	L-T	4.0	H4													
			T-L	4.0	H0													
	T7651	R.T.	L-T	20.0	71.2													
			T-L	4.0	71.0													
				20.0	70.5													
7475	T61	R.T.	L-T	16.0	H6													
		88	L-T	16.0	H5.6													
		R.T.	T-L	16.0	L2													
		88	T-L	16.0	H1.6													
				16.0	H4													
		R.T.	L-T	16.0	H4													
		88	L-T	16.0	H4													
		R.T.	T-L	16.0	H1													
		88	T-L	16.0	H1													

TABLE 8.0.3.2 (con't)

PLANE STRESS AND TRANSITIONAL FRACTURE TOUGHNESS
OF 7000 SERIES ALUMINUM ALLOYS (WITHOUT BUCKLING CONSTRAINTS)

ALLOY	CONDITION/ HT	TEST TEMP (°F)	SPECIMEN ORIENT WIDTH	FIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	K _c (Ksi/in)										
7050 (Al-Li)	T61	R.T.	L-T	70	0.010	0.020	0.030	0.040	0.063	0.080-0.090	0.125	0.160	0.180	0.250	0.500	1.000
		R.T.	T-L	68												
	T761	R.T.	L-T	64.5												
		R.T.	T-L	63												

Mean/Standard Deviation (Number of Specimens)

TABLE 8.0.4.1

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION L-T ENVIRONMENT LAB AIR AT R T
 STRESS RATIO 0.00-0.10 FREQUENCY 0.10-30.00 HZ

ALLOY CONDITION/HIT PRODUCT FORM STRESS RATIO FREQUENCY FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) = 2.5 5.0 10.0 20.0 50.0 100.0

7001	T75	SHEET	0.05	2.00		60.7
7005	T6	SHEET	0.05	2.00	6.74	28.5
7010	T73651	PLATE	0.10	20.00	25.00	2.83 56.5
7049	T73511-HIGH PURITY	EXTRUSION	0.10	30.00		7.84
	T73511-LOW PURITY	EXTRUSION	0.10	30.00		7.32
	T73511-MEDIUM PURITY	EXTRUSION	0.10	30.00		3.44
7050	T73511-HIGH PURITY	EXTRUSION	0.10	30.00		5.93
	T736	FORGING	0.10	3.00-10.00		11.9 58.7
	T73651	PLATE	0.10	5.00-10.00		7.68 47.3
	T76	SHEET	0.00	13.30		7.60 40.1
	T7651	PLATE	0.02	1.00-20.00	580	8.04 22.9

TABLE 8.0.4.1 (con't)

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS -

SPECIMEN ORIENTATION L-T
 STRESS RATIO 0.00-0.10

ENVIRONMENT LAB AIR AT R T
 FREQUENCY 0.10-30.00 HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN))
					2.5 5.0 10.0 20.0 50.0 100.0
7075	T6	SHEET	0.02	1.00	103
	T6	SHEET	0.02	3.00	92.8
	T6	SHEET	0.02	10.00	14.0 60.0 5417
	T6	SHEET	0.02	10-30.00	11.7 54.5 20651
	T651	PLATE	0.02	1.00-30.00	1.64 1.18 66.6
	T651	PLATE	0.02	10-30.00	8.32 58.5
	T6511	EXTRUSION	0.01	30.00	97.6 72.1
	T73	PLATE	0.05	20.00	0.564 561 11.7
	T7351	PLATE	0.02	10-20.00	293 5.65 59.4
	T7351	PLATE	0.02	10.00	3.95 41.4
	T7351	PLATE	0.02	10.00	5.09 46.0 1538
	T7351	PLATE	0.02	1.00	5.04 44.0
	T73511-HIGH PURITY	EXTRUSION	0.10	30.00	6.39 31.3
	T73511-LOW PURITY	EXTRUSION	0.10	30.00	8.14
	T73511-MEDIUM PURITY	EXTRUSION	0.10	30.00	7.14
	T7352	BILLET	0.02	1.00-30.00	32.5

TABLE 8.0.4.1 (con't)

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION L-T ENVIRONMENT: LAB AIR AT R.T
 STRESS RATIO 0.00-0.10 FREQUENCY: 0.10-30 00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =
					2 5 5 0 10 0 20 0 50 0 100 0
7079	T6	SHEET	0.05	2.00	64.8
	T6	BILLET	0.02	1.00-30.00	10.7
	T651	SHEET	0.05	2.00	14.0 92.6

TABLE 8.0.4.1 (con't)

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION L-T
 STRESS RATIO 0.00-0.10
 ENVIRONMENT LAB AIR AT R.T.
 FREQUENCY 0.10-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =					
					2.5	5.0	10.0	20.0	50.0	100.0
7149	T73511	EXTRUSION	0.01	1.00-20.00	1.64	8.32	57.9			
	T736	FORGING	0.02	10.00	9.87	56.8				
	T73652	FORGING	0.02	1.00-20.00	7.92	33.3				
	T73652	FORGING	0.02	1.00-18.00	8.06	8.03				
7178	T6	SHEET	0.02	10.00-14.00	11.9	89.9				
	T6	SHEET	0.02	1.00-5.00	12.6	109				
	T651	SHEET	0.02	10-12.00	9.23	15.4	99.6			
	T651	PLATE	0.00	10-20.00	7.99	13.1	56.8			
	T651	PLATE	0.02	10-20.00	9.80	15.4	107			
T76	SHEET	0.02	20.00	6.05	7.76	58.1	2653			

TABLE 8.0.4.1 (con't)

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

STRESS RATIO 0 00-0 10

ENVIRONMENT LAB AIR AT R T

FREQUENCY 0 10-30 00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN)) =					
					2 5	5 0	10 0	20 0	50 0	100 0
7475	T61	PLATE	0 10	20 00			6 87			
	T6151	SHEET	0 10	20 00		40 7	5 52			
	T7351	PLATE	0 02	10- 20 00	216	5 00	37 1	2520		
	T7351	PLATE	0 10	20 00		5 55				
	T761	SHEET	0 10	20 00		5 41	33 1			
	T7651	SHEET	0 00	2 00- 30 00	254	4 56	42 3			
7475(Al CLAD)	T7651	PLATE	0 00	3 00 30 00		3 93	47 6	508		
	T61	SHEET	0 00	13 30		5 71	32 7			

TABLE 8.0.4.2

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION T-L ENVIRONMENT LAB AIR AT R T
 STRESS RATIO 0 00-0 10 FREQUENCY 0 10-30 00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT.IN) ²
					2 5 5 0 10 0 20 0 50 0 100 0
7010	T73651	PLATE	0 10	20 00-25 00	6 15 85 4
7049	T73511-HIGH PURITY	EXTRUSION	0 10	30 00	7 8 1
	T73511-LOW PURITY	EXTRUSION	0 10	30 00	9 13
	T73511-MEDIUM PURITY	EXTRUSION	0 10	30 00	8 15
7050	T73511-HIGH PURITY	EXTRUSION	0 10	30 00	3 9 7
	T736	FORGING	0 10	10 00	6 7 6 101
	T73651	PLATE	0 10	1 00-10 00	8 4 5 49 4
7075	T6	SHEET	0 00	13 30	5 4 5 42 6
	T73511-HIGH PURITY	EXTRUSION	0 10	30 00	4 6 6 36 1
	T73511-LOW PURITY	EXTRUSION	0 10	30 00	8 1 2
7352	T7352	PLATE	0 02	10 00	4 7 4 6 2 8 66 2 40 9 5
	T7352	PLATE	0 02	10 00	1 0 8 1 1 1 1
	T7352	FORGING	0 02	10 00	1 8 6 1 4 4 1 2 6
T7352	FORGING	0 02	10 00	2 7 5	

TABLE 8.0.4.2 (con't)

COMPARISON OF FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS OF THE STRESS INTENSITY FACTOR FOR ALUMINUM ALLOYS

TEST CONDITIONS

SPECIMEN ORIENTATION T-L
 STRESS RATIO 0.00-0.10
 ENVIRONMENT LAB AIR AT R T
 FREQUENCY 0.10-30.00HZ

ALLOY	CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQUENCY	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE) FOR DELTA K LEVELS (KSI SQRT(IN))				
					2.5	5.0	10.0	20.0	50.0
7075(AlCLAD)	T6	SHEET	0.00	13.30		6.99	68.3		
	T6	SHEET	0.05	30.00	450				
7079	T6	FORGING	0.05	9.00	387	7.81	42.8		
7149	T73511	EXTRUSION	0.10	1.00-20.00	1.97	10.8	152.0		
7175	T73652	FORGING	0.02	10-20.00		10.7	45.4		
7178	T651	PLATE	0.00	20.00	478	11.5	85.2		
7475	T6151	SHEET	0.10	20.00		6.22	54.5		
	T761	SHEET	0.10	20.00		4.36	43.8		
7475(AlCLAD)	T61	SHEET	0.00	13.30		8.56	19.9		
	T761	SHEET	0.00	13.30		5.53	31.0		

TABLE 8.0.5

STRESS CORROSION CRACKING THRESHOLD DATA FOR 7000 SERIES ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/HT	PRODUCT FORM	SPECIMEN ORIENTATION	ENVIRONMENTS						K _{Isc} (Ksi $\sqrt{in.}$)
				INDUSTRIAL ATMOSPHERE	SEACOAST ATMOSPHERE	SALT DICHROMATE ACETATE	SIMP TANK WATER	3.5% NaCl	SHOP CLEANING SOLVENT	
7005	T63	P	S-L						28.0	
7007	T6-Repaired	P	S-L						8.7	
	Weld-Fusion Line									
	T6-Repaired	P	S-L						16.3	
	Weld-Heat Affected Zone									
	T6-Repaired	P	S-L						10.6	
	Weld Center Line									
7010	173651	P	T-L						32.5(2)	
			S-L						17.9	
7029	173	F	S-L						17.0	
		E	L-S						20.4	
	173 Integrally	E	L-S						20.3	
		Stiffened	S-L						26.7	
	17352	F	L-T						19.4	27.6
			L-L						21.0	19.3(2)
7030	173651	P	S-L						17.3(2)	
			L-L						27.8	29.1
7075	T6	P	S-L						19.0	
	1651	P	L-L						26.3	
	17351	P	S-L	10.0			5.0		17.0	
			L-L						23.9	
	173511	L-B	S-L	20.0			19.0		21.0	35.6
17352	L	L-L						18.0		
17651	P	S-L						12.8(4)		

TABLE 8.0.5 (con't)

STRESS CORROSION CRACKING THRESHOLD DATA FOR 7000 SERIES
ALUMINUM ALLOYS AT ROOM TEMPERATURE

ALLOY	CONDITION/HT	PRODUCT FORM	SPECIMEN ORIENTATION	ENVIRONMENTS					K _{Isc} (Ksi √In.)
				INDUSTRIAL ATMOSPHERE	SEACOAST ATMOSPHERE	SALT DICHROMATE ACETATE	SUMP TANK WATER	SHOP CLEANING SOLVENT	
7070	16	P	S-L	9.0	9.0	6.0		6.6(4)	
	1651	P	S-L					3.0	
7170	1735-14	F	S-L					25.4(9)	
	1736	F	L-L					30.6	
		F	S-L					18.7	
	173652	F	L-L					27.6(2)	
7050	17351	P	S-L				22.0		
		P	L-L				26.6		
	17351	P	L-L				30.9		
			L-L				30.8		

TABLE 8.1.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 7051 AT ROOM TEMPERATURE

CONDITION	MEAN K _{IC} ± STANDARD DEVIATION		NUMBER OF SPECIMENS
	(KSI)	(GRT(IN))	
T-1	24.1 ± 1.7 (4)	L-1	20 7 ± 1 8 (5)
		I-1	
		S-1	

TABLE 8.1.2.1

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	SPECIMEN		W	THICK (IN)	DESIGN	CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)				B	A									
T75	P	1.37	70.6	L-T	R.T.	3.000	1.381	NB	1.463	0.24	22.00	1973	86213			
		1.37	70.6			3.000	1.382	NB	1.560	0.27	23.40	1973	86213			
		1.37	72.2			3.000	1.360	NB	1.584	0.32	25.80	1973	86213			
T75		1.37	72.2			3.000	1.364	NB	1.513	0.30	25.00	24	1/	1.7	1973	86213
	P	1.37	69.6	T-L	R.T.	3.000	1.376	NB	1.587	0.23	21.30	1973	86213			
		1.37	69.6			3.000	1.377	NB	1.532	0.29	23.60	1973	86213			
		1.37	70.6			3.000	1.360	NB	1.564	0.17	19.60	1973	86213			
T75		1.37	71.6			3.000	1.364	NB	1.463	0.19	19.90	1973	86213			
		1.37	71.6			3.000	1.381	NB	1.584	0.18	19.10	20.7/	1.8	1973	86213	
	P	1.37	65.9	S-L	88	1.000	0.500	CT	0.494	0.14	15.80	1973	86213			
	1.37	65.9			1.000	0.500	CT	0.478	0.14	15.60	1973	86213				
	1.37	65.9			1.000	0.500	CT	0.510	0.15	15.90	15.8/	0.2	1973	86213		

TABLE 8.1.2.2

CONDITION	PRODUCT-- FORM	THICK (IN)	TEST SPEC OR TEMP (F)	YIELD STR (KSI)	ALUMINUM				7001				K(C)				K(C) STAN MEAN DEV (KSI*SQRT IN)	K(C) STAN MEAN DEV (KSI*SQRT IN)	REFER DATE
					SPECIMEN--		CRACK LENGTH		GROSS STRESS		K(APP)		STAN		K(C)				
					WIDTH (IN)	THICK (IN)	INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	2A(O) 2A(F)	S(O) S(MAX)	MEAN (KSI*SQRT IN)	DEV (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	DEV (KSI*SQRT IN)			
T75	S	0.12	R.T.	66.1	3.000	0.119	1.070	1.480	---	32.90	46.34	---	59.35*	---	59.35*	---	1973 86213		
		0.12		67.7	3.000	0.119	1.090	1.360	---	32.00	45.64	---	53.76*	---	53.76*	---	1973 86213		
		0.12		66.1	3.000	0.125	1.060	1.290	---	34.40	48.15*	---	55.43*	---	55.43*	---	1973 86213		
		0.12		66.1	3.000	0.124	1.110	1.650	---	33.30	48.10	---	66.52*	---	66.52*	---	1973 86213		
		0.12		66.1	3.000	0.122	1.080	1.350	---	31.00	43.94	---	51.77*	---	51.77*	---	1973 86213		
		0.12		67.7	3.000	0.122	1.110	1.450	---	33.10	47.81	---	58.65*	---	58.65*	---	1973 86213		
		0.12		67.7	3.000	0.125	1.110	1.320	---	32.90	47.52	---	53.97*	---	53.97*	---	1973 86213		
		0.12		67.7	3.000	0.126	1.100	1.380	---	30.90	44.35	---	52.53*	---	52.53*	---	1973 86213		
		0.12		69.3	3.000	0.127	1.080	1.240	---	32.60	46.21	---	50.98*	---	50.98*	---	1973 86213		
		0.12		69.3	3.000	0.125	1.090	1.400	---	33.40	47.64	---	57.46*	---	57.46*	---	1973 86213		
		0.12		69.3	3.000	0.124	1.090	1.340	---	32.20	45.93	---	60.20*	---	60.20*	---	1973 86213		
		0.12		69.3	3.000	0.126	1.090	1.410	---	32.80	46.79	---	56.76*	---	56.76*	---	1973 86213		
T75	P	1.00	R.T.	70.6	20.000	1.000	7.000	8.420	---	9.10	32.68	---	37.25	---	37.25	---	1973 86213		
		1.00		70.6	20.000	1.000	7.000	8.650	---	6.40	22.98	---	26.75	---	26.75	---	1973 86213		
		1.00		70.6	20.000	1.000	7.000	8.590	---	9.40	33.76	---	39.07	---	39.07	---	1973 86213		
		1.00		70.6	20.000	1.000	7.000	8.420	---	9.50	34.12	---	38.89	---	38.89	---	1973 86213		
		1.00		70.6	20.000	1.000	7.000	8.420	---	9.00	32.32	---	36.84	---	36.84	---	1973 86213		
		1.00		70.6	20.000	1.000	7.000	7.650	---	6.40	22.98	---	24.43	---	24.43	---	1973 86213		
		1.00		70.6	20.000	1.000	7.000	8.050	---	6.10	21.91	---	24.15	---	24.15	---	1973 86213		
		1.00		70.6	20.000	1.000	7.000	7.720	---	6.70	24.06	---	25.74	---	25.74	---	1973 86213		
		1.00		72.2	20.000	1.000	7.000	8.500	---	8.60	30.88	---	35.46	---	35.46	---	1973 86213		
		1.00		72.2	20.000	1.000	7.000	8.650	---	9.10	32.68	---	38.03	---	38.03	---	1973 86213		
		1.00		72.2	20.000	1.000	7.000	8.420	---	9.00	32.32	---	36.84	---	36.84	---	1973 86213		
		1.00		72.2	20.000	1.000	7.000	8.020	---	8.40	30.17	---	33.17	---	33.17	---	1973 86213		
T75	S	0.12	R.T.	67.7	3.000	0.124	1.210	1.240	---	22.00	33.79	---	34.40	---	34.40	---	1973 86213		
		0.12		67.7	3.000	0.124	1.130	1.250	---	24.60	35.97	---	38.70	---	38.70	---	1973 86213		
		0.12		67.7	3.000	0.125	1.120	1.280	---	28.70	41.71	---	45.97	---	45.97	---	1973 86213		
		0.12		67.7	3.000	0.125	1.130	1.240	---	24.60	35.97	---	38.47	---	38.47	---	1973 86213		
		0.12		68.0	3.000	0.128	1.140	1.400	---	24.20	35.61	---	41.63	---	41.63	---	1973 86213		
		0.12		68.0	3.000	0.128	1.110	1.320	---	24.00	34.66	---	39.37	---	39.37	---	1973 86213		
		0.12		68.0	3.000	0.126	1.120	1.220	---	24.80	36.04	---	38.32	---	38.32	---	1973 86213		
		0.12		68.0	3.000	0.126	1.160	1.370	---	25.20	37.54	---	40.12	---	40.12	---	1973 86213		
		0.12		68.6	3.000	0.123	1.090	1.220	---	25.90	36.94	---	40.02	---	40.02	---	1973 86213		

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 8.1.2.2 (Con't)

CONDITION	ALUMINUM		7001		K(C)		CRACK LENGTH CROSS STRESS				K(APP) STAN		K(C) STAN			
	--PRODUCT-- FORM	THICK (IN)	TEST SPEC OR STR (KSI)	YIELD (KSI)	--SPECIMEN--		ONSET (KSI)	MAX (KSI)	S(O) S(MAX)	K(APP) (KSI*SQRT IN)	MEAN DEV	K(C) (KSI*SQRT IN)	MEAN DEV	DATE	REFER	
					WIDTH (IN)	THICK (IN)										INIT (IN)
175	S	0.12	R T	T-L	68.6	3.000	0.123	1.100	1.270	---	24.10	34.59	38.37	1973	86213	
		0.12			68.6	3.000	0.124	1.110	1.300	---	24.80	35.82	40.20	1973	86213	
		0.12			68.6	3.000	0.124	1.090	1.300	---	23.80	33.95	36.0/ 2.1	39.5/ 2.7	1973	86213
175	P	1.00	R T	T-L	69.6	20.000	1.000	7.000	7.650	---	7.40	26.57	28.24	1973	86213	
		1.00			69.6	20.000	1.000	7.000	7.900	---	7.20	25.86	28.12	1973	86213	
		1.00			69.6	20.000	1.000	7.000	8.050	---	7.10	25.50	28.11	1973	86213	
		1.00			69.6	20.000	1.000	7.000	8.050	---	7.00	25.14	27.71	1973	86213	
		1.00			70.6	20.000	1.000	7.000	8.330	---	8.30	29.81	33.70	1973	86213	
		1.00			70.6	20.000	1.000	7.000	7.950	---	7.90	28.37	30.99	1973	86213	
		1.00			70.6	20.000	1.000	7.000	8.320	---	8.10	29.09	32.86	1973	86213	
		1.00			70.6	20.000	1.000	7.000	8.460	---	8.00	28.73	32.87	1973	86213	
		1.00			71.3	20.000	1.000	7.000	7.900	---	6.90	24.78	26.95	1973	86213	
		1.00			71.3	20.000	1.000	7.000	7.000	---	6.50	23.34	23.34	1973	86213	
		1.00			71.3	20.000	1.000	7.000	8.050	---	6.60	23.70	26.13	1973	86213	
		1.00			71.3	20.000	1.000	7.000	7.900	---	6.40	22.98	26.2/ 2.4	28.7/ 3.3	1973	86213

BUCKLING OF CRACK EDGES NOT RESTRAINED

TABLE 8.1.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.1.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7001
CONDITION: T75

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K MIN	A:	10.34	8.13		
	B:				
	C:				
	D:				
		13.00	18.1		
		16.00	32.0		
		20.00	60.7		
DELTA K MAX	A:	20.63	67.3		
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 4.22
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T75
 FORM: 0.16" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.05
 FREQUENCY: 2.00

YIELD STRENGTH: 72.2 KSI
 ULT. STRENGTH: 79.6 KSI
 SPECIMEN THK: 0.163"
 SPECIMEN WIDTH: 9.010- 9.030"
 REFERENCES: 86734

ALUM.
ALLOY

7001

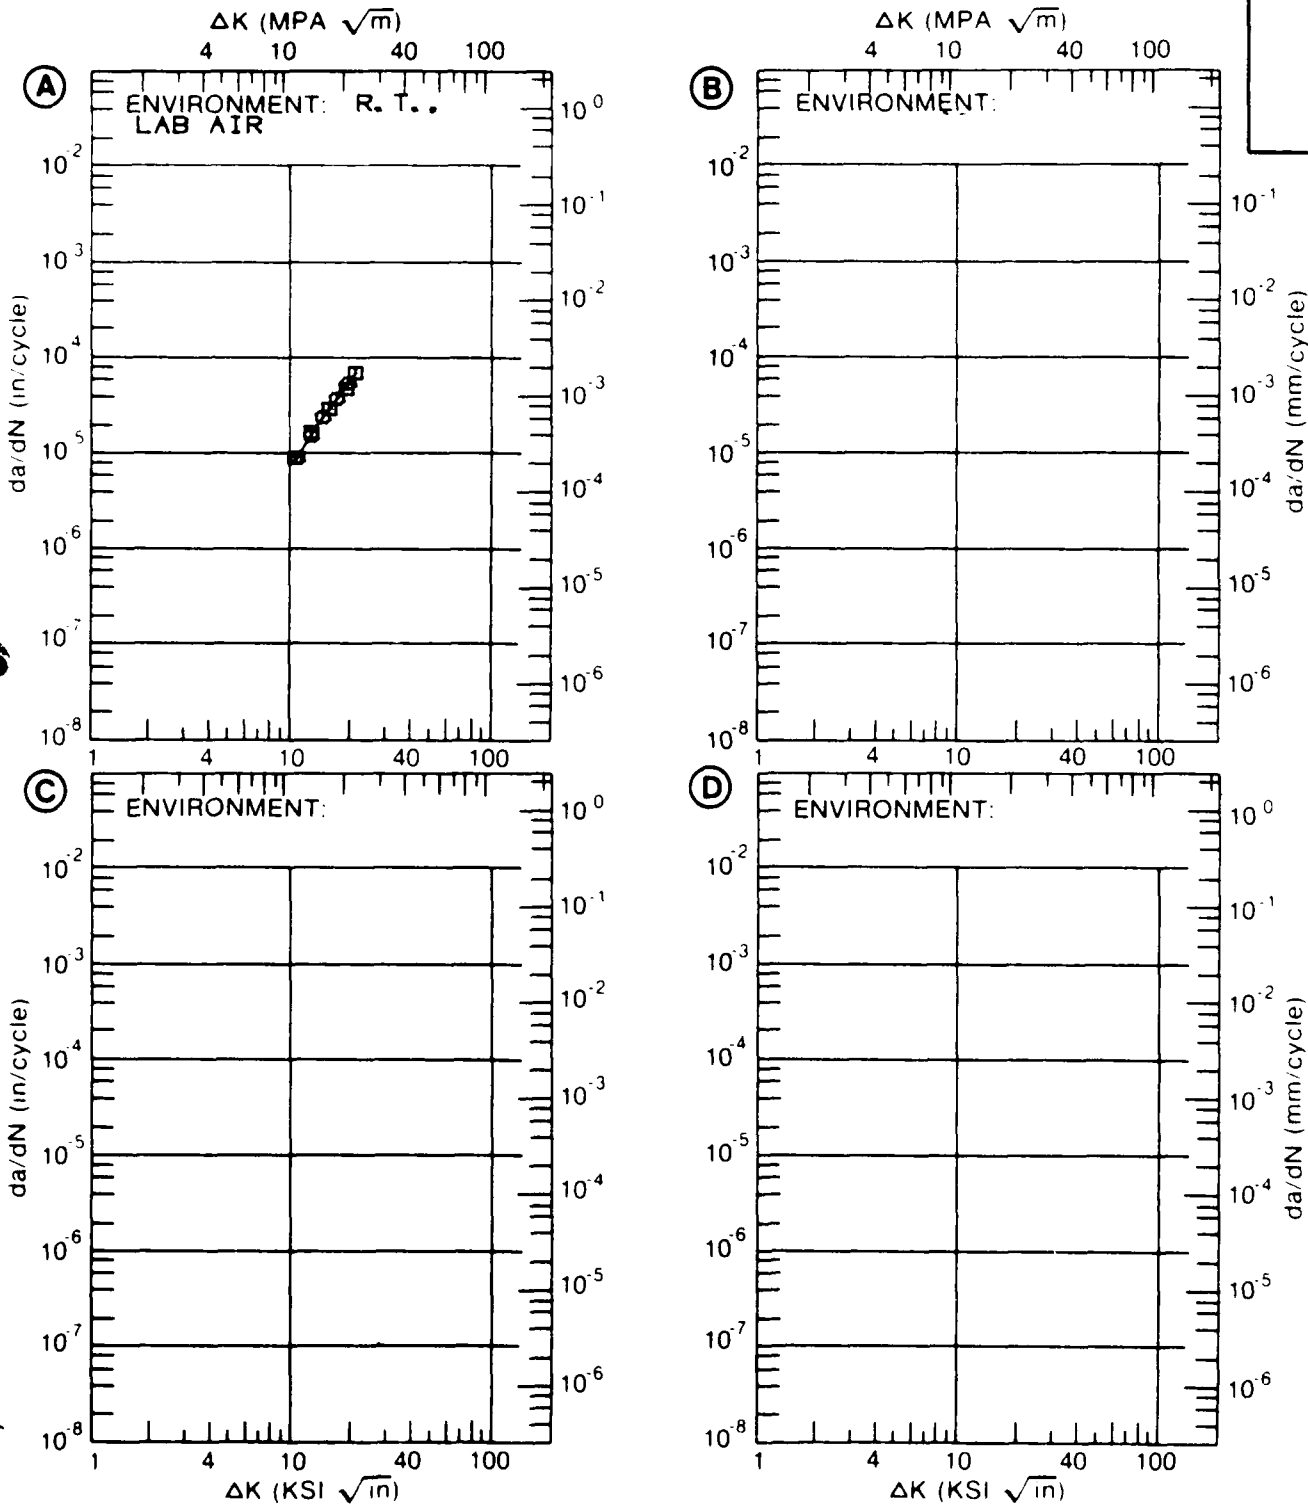


Figure 8.1.3.1
 8.1-7

TABLE 8.2.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 7005 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)
		PLATE
	I-II	I-II
	9-L	9-L
16351	40.7 ± 1.0 (2)	39.7 ± 0.9 (3)

TABLE 8.2.2.1

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT (F)	THICK (IN)	SPECIMEN THICK (IN)	DESIGN	K(1C)		DATE	REFER
	7005	K(1C)						CRACK LENGTH (IN)	2.5* (IN)		
	FORM (IN)	W (IN)				B (IN)		A (IN)			
T6351	P	3.00	48.2	R. T.	3.00	6.000	2.953 NB	2.922	2.42	47.40	1973 86213
		3.00	48.2			6.000	2.958 NB	2.927	2.28	46.00	1973 86213
T6351	P	3.00	49.0	R. T.	3.00	6.000	2.958 NB	2.960	1.56	38.70	1973 86213
		3.00	49.0			6.000	2.964 NB	3.107	1.67	40.00	1973 86213
		3.00	49.0			6.000	2.962 NB	2.943	1.71	40.50	1973 86213
T6351	P	3.00	49.0	82	3.00	4.500	2.250 NB	2.260	1.72	40.60	1973 86213
T6351	P	3.00	47.5	88	3.00	2.500	1.250 CT	1.209	0.84	27.60	1973 86213
		3.00	47.5			2.500	1.250 CT	1.196	0.84	27.50	1973 86213

TABLE 8.2.2.2

CONDITION	ALUMINUM	7005	K(C)	CRACK LENGTH CROSS STRESS										K(C) STAN MEAN DEV (KSI*SQRT IN)	K(C) STAN MEAN DEV (KSI*SQRT IN)		
				---SPECIMEN---		INIT		FINAL		ONSET		MAX					
				WIDTH (IN)	THICK (IN)	(IN)	(IN)	(IN)	(IN)	(KSI)	(KSI)	(KSI)	(KSI)				
				W	B	2A(D)	2A(F)	S(O)	S(MAX)								
BUCKLING OF CRACK EDGES NOT RESTRAINED																	
T6	S	0.06	R.T.	L-T	43.4	3.000	0.064	1.113	---	---	28.60	41.36*	---	---	---	---	1973 86213
		0.06			43.4	3.000	0.064	1.115	---	---	29.10	42.13*	---	---	---	---	1973 86213
T6	S	0.12	R.T.	L-T	45.1	3.000	0.125	1.123	---	---	29.80	43.36*	---	---	---	---	1973 86213
		0.12			45.1	3.000	0.125	1.120	---	---	29.60	43.02*	---	---	---	---	1973 86213
T6	P	0.25	R.T.	L-T	49.8	4.000	0.258	1.597	---	---	32.40	57.00*	---	---	---	---	1973 86213
		0.25			49.8	4.000	0.258	1.597	---	---	32.20	56.65*	---	---	---	---	1973 86213
T6	S	0.06	R.T.	T-L	44.0	3.000	0.064	1.183	---	---	28.60	43.18*	---	---	---	---	1973 86213
		0.06			44.0	3.000	0.064	1.147	---	---	28.80	42.50*	---	---	---	---	1973 86213
T6	S	0.12	R.T.	T-L	45.6	3.000	0.125	1.110	---	---	30.10	43.47*	---	---	---	---	1973 86213
		0.12			45.6	3.000	0.125	1.123	---	---	30.00	43.65*	---	---	---	---	1973 86213
T6	P	0.25	R.T.	T-L	50.6	4.000	0.258	1.598	---	---	32.40	57.05*	---	---	---	---	1973 86213
		0.25			50.6	4.000	0.258	1.603	---	---	32.10	56.63*	---	---	---	---	1973 86213
BUCKLING OF CRACK EDGES NOT RESTRAINED																	
T6351	P	1.00	R.T.	L-T	47.2	20.000	1.023	2.610	---	---	40.10	82.06*	---	---	---	---	1973 86213
		1.00			47.2	20.000	1.023	7.000	---	---	29.70	106.66*	---	---	---	---	1973 86213
		1.00			47.2	20.000	1.023	4.880	---	---	34.50	99.18*	---	---	---	---	1973 86213
T6351	P	1.00	R.T.	T-L	46.5	20.000	1.023	7.000	---	---	28.00	100.95*	---	---	---	---	1973 86213
		1.00			46.5	20.000	1.023	2.610	---	---	38.10	77.76*	---	---	---	---	1973 86213
		1.00			46.5	20.000	1.023	4.850	---	---	32.60	93.39*	---	---	---	---	1973 86213

*NOTE - NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV.

TABLE 8.2.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.2.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7005
CONDITION: T6
ENVIRONMENT: R T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.05			
DELTA K	A: 6.18	1.78			
MIN	B:				
	C:				
	D:				
	7.00	2.69			
	8.00	3.95			
	9.00	5.31			
	10.00	6.74			
	13.00	11.5			
	16.00	17.4			
	20.00	28.5			
	25.00	52.4			
DELTA K	A: 26.14	60.3			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 12.16
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 4
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T6
 FORM: 0.16" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 2.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 49.0 KSI
 ULT. STRENGTH:
 SPECIMEN THK: 0.100- 0.162"
 SPECIMEN WIDTH: 3.000- 14.040"
 REFERENCES: 86734

ALUM. ALLOY
7005

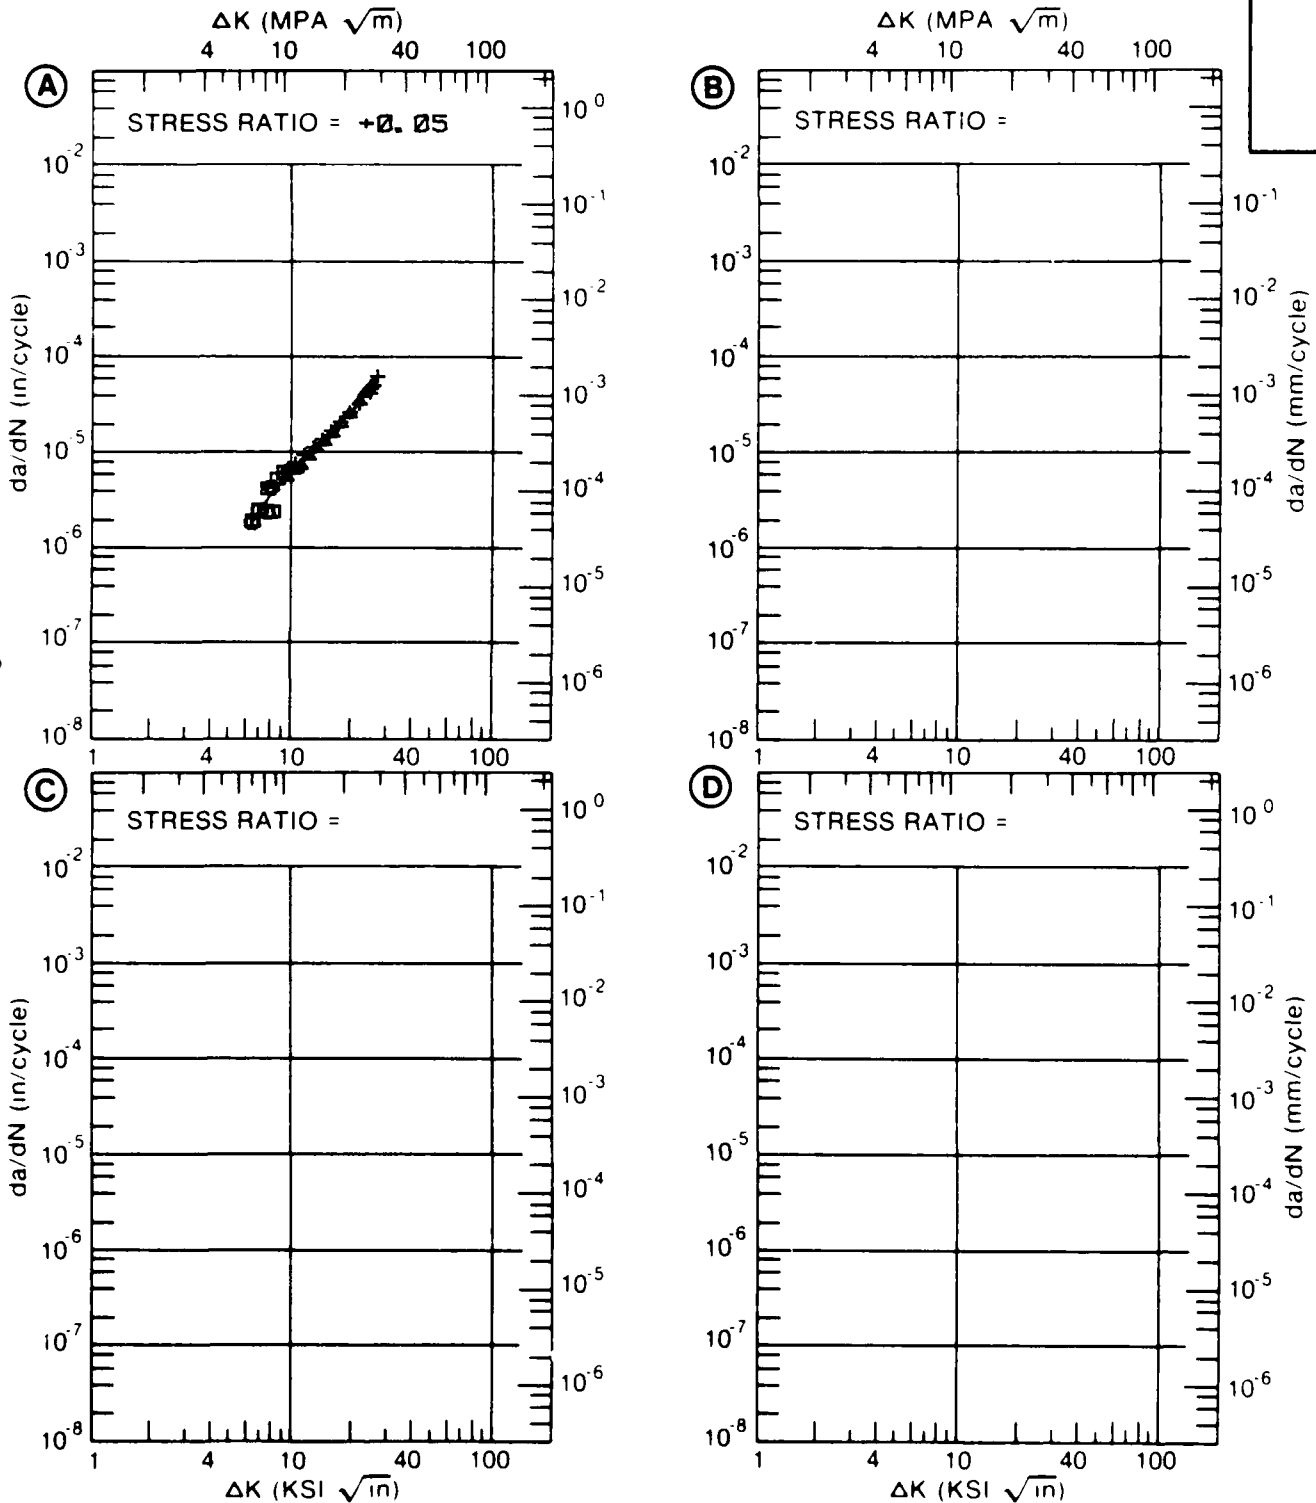


Figure 8.2.3.1

TABLE 8.2.3.2

CONDITION	ALUMINUM		7005		K (ISCC)		STAN DEV	TEST TIME (MIN)	DATE REFER						
	--PRODUCT-- FORM THICK (IN)	TEST TEMP (F)	OR STR (KSI)	YIELD	ENVIRONMENT	WIDTH (IN)				THICKNESS (IN)	DESIGN (*SC)	CRACK LENGTH (IN)	K (ISCC)	MEAN	
T63	P	1.00	R T	S-L	46 0 3 5	PCT	NACL	4.000	1.000	DCB	42.00	28.00	-----	1968	84331

TABLE 8.3.3.1

CONDITION	PRODUCT		TEST SPEC YIELD STR (KSI)	ENVIRONMENT	SPECIMEN		WIDTH (IN)	THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	K (ISCC)	K (ISCC)	MEAN (KSI)	STAN DEV	TEST TIME (MIN)	DATE REFER		
	FORM	THICK (IN)			THICK (IN)	THICK (IN)											THICK (IN)	THICK (IN)
T6 OVERHEATED WELD CENTER LINE	P	1.00	R T S-L	37.2	3.5	PCT	NAACL	2.500	1.000	WDL	----	35.00	> 11.00		4320	1970	80073	
T6 REPAIRED WELD FUSION LINE	P	1.00	R T S-L	----	3.5	PCT	NAACL	2.500	1.000	WDL	----	41.00	8.70	>	4320	1970	80073	
T6 REPAIRED WELD HEAT AFF ZONE	P	1.00	R T S-L	----	3.5	PCT	NAACL	2.500	1.000	WDL	----	42.00	16.30	>	4320	1970	80073	
T6 REPAIRED WELD CENTER LINE	P	1.00	R T S-L	----	3.5	PCT	NAACL	2.500	1.000	WDL	----	27.00	10.60	>	4320	1970	80073	
T6 WELD CENTER LINE	P	1.00	R T S-L	39.9	3.5	PCT	NAACL	2.500	1.000	WDL	----	42.00	< 12.00	>	4320	1970	80073	
T6 WELD FUSION LINE	P	1.00	R T S-L	39.9	3.5	PCT	NAACL	2.500	1.000	WDL	----	42.00	< 11.00		4320	1970	80073	
T6 WELD HEAT AFF ZONE	P	1.00	R T S-L	40.4	3.5	PCT	NAACL	2.500	1.000	WDL	----	40.00	> 15.00	>	4200	1970	80073	

TABLE 8.4.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF
ALUMINUM ALLOY 7010 AT ROOM TEMPERATURE

CONDITION HT	MEAN K _{IC} ± STANDARD DEVIATION		PLAQUE	NUMBER OF SPECIMENS
	KSI	(IN)		
T/MSI	37.5	± 4.6	I-L	(4)
	27.9	± 2.8	I-L	(5)
			S-L	23.1 ± 0.5 (2)

TABLE 8.4.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7010

TEST CONDITIONS

SPECIMEN ORIENTATION T

ENVIRONMENT LAB AIR AT R T

SPECIMEN HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
173651	PLATE	0.10	20.00-20.00		0.25	2.83	56.5			
173651	PLATE	0.30	10.00-20.00		0.46	8.19				
173651	PLATE	0.50	10.00-20.00		1.03	11.7				
173651	PLATE	0.65	10.00-20.00		2.01	17.8				
T 1	PLATE	0.80	10.00-20.00		3.25					

TABLE 8.4.2.1

CONDITION	--PRODUCT--		TEST SPECIMEN		YIELD STRENGTH (KSI)	ALUMINUM		CRACK LENGTH (IN)	2.5* (K(IIC)/TYS)**2 (IN)	K(IIC) (KSI*SQRT IN)	K(IIC) MEAN DEV	DATE	REFER		
	FORM	THICK (IN)	TEMP (F)	ORIENT		WIDTH (IN)	7010								
							W							B	
T73651	P	2.00	R.T.	L-T	63.2	1.500	0.750	CT	0.782	0.57	30.20	1980	BL001		
		2.00			63.2	1.500	0.750	CT	0.777	0.52	28.90	1980	BL001		
		2.00			64.4	3.000	1.500	CT	---	0.86	37.80	1980	UD003		
T73651	P	2.00	250	L-T	64.4	3.000	1.500	CT	---	0.83	37.10	33.5/	4.6	1980	UD003
		2.00			64.4	3.000	1.500	CT	---	0.94	39.40	1980	UD003		
		2.00			64.4	3.000	1.500	CT	---	0.87	38.00	38.7/	1.0	1980	UD003
T73651	P	2.00	R.T.	T-S	62.9	1.500	0.750	CT	---	0.58	30.30	1980	UD003		
		2.00			62.9	1.500	0.750	CT	---	0.64	31.80	31.1/	1.1	1980	UD003
		2.00			62.9	1.500	0.750	CT	---	0.56	29.90	1980	UD003		
T73651	P	2.00	R.T.	T-L	62.9	1.500	0.750	CT	---	0.53	29.00	1980	UD003		
		2.00			62.9	1.500	0.750	CT	---	0.60	30.80	1980	UD003		
		2.00			63.6	1.500	0.750	CT	0.766	0.38	24.80	1980	BL001		
T73651	P	2.00	250	T-L	63.6	1.500	0.750	CT	0.786	0.38	24.90	27.9/	2.8	1980	BL001
		2.00			62.9	1.500	0.750	CT	---	0.50	28.00	1980	UD003		
		2.00			65.0	1.500	0.750	CT	---	0.30	22.70	1980	UD003		
T73651	P	2.00	R.T.	S-L	65.0	1.500	0.750	CT	---	0.32	23.40	23.1/	0.5	1980	UD003
		2.00			65.0	1.500	0.750	CT	---	0.32	23.40	23.1/	0.5	1980	UD003

TABLE 8.4.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.4.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7010			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E=+ 250 AIR		
DELTA K MIN	A: 5.00	.386			
	B: 3.73		.186		
	C:				
	D:				
	4.00		.253		
	5.00		.648		
	6.00	.886	1.60		
	7.00	2.11	3.70		
	8.00	3.98	7.80		
	9.00	6.40	13.9		
	10.00	9.21	20.4		
	13.00	18.6	32.4		
	16.00	27.5	42.5		
	20.00	38.0	84.5		
	25.00	50.0			
	30.00	74.7			
DELTA K MAX	A: 31.27	94.6			
	B: 20.31		91.0		
	C:				
	D:				
ROOT MEAN SQUARE		12.77	7.88		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25				
	1.25-2.0				
	>2.0				

CONDITION/HT: T73651
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-S
 STRESS RATIO: +0.10
 FREQUENCY: 20.00- 25.00 HZ

YIELD STRENGTH: 64.4 KSI
 ULT. STRENGTH: 73.7 KSI
 SPECIMEN THK: 0.300"
 SPECIMEN WIDTH: 1.500"
 REFERENCES: UD003

ALUM. ALLOY
7010

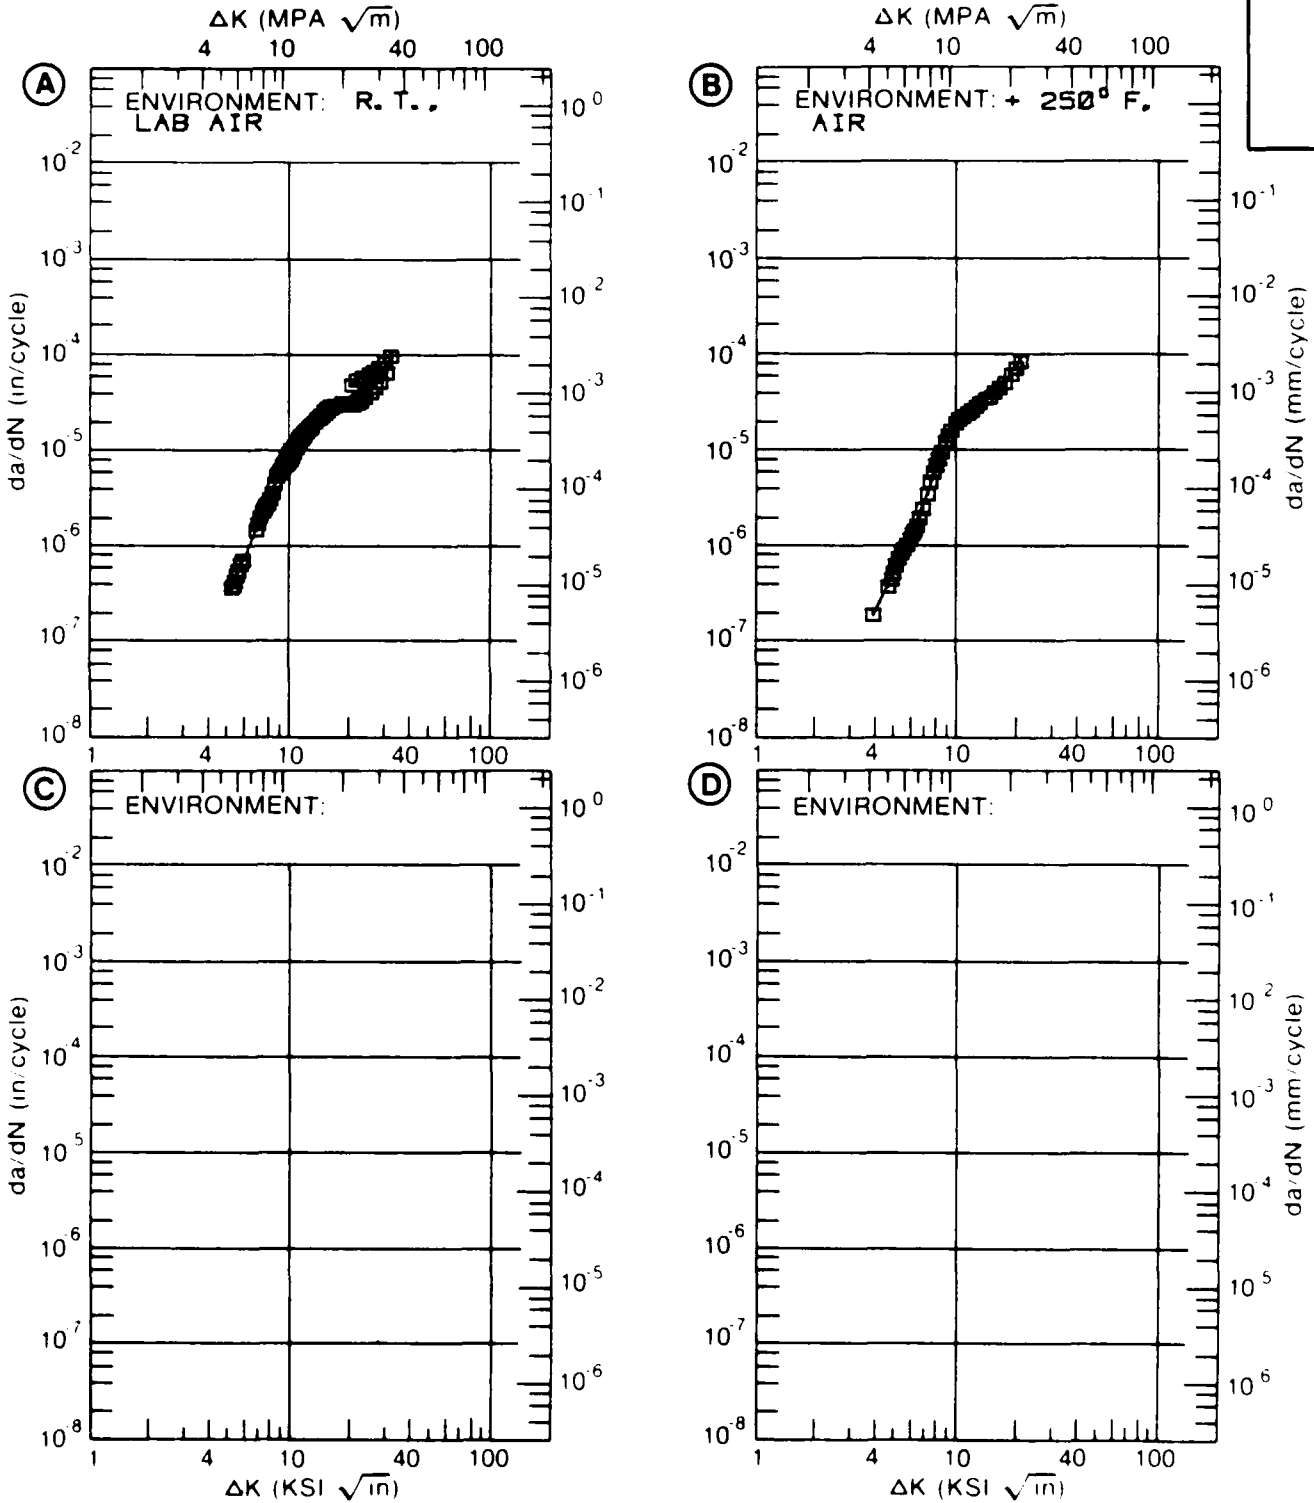


Figure 8.4.3.1

TABLE 8.4.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.4.3.2 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7010
CONDITION: T73651
ENVIRONMENT: R. T., LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A R=+0.30	B R=+0.50	C R=+0.65	D R=+0.80
DELTA K MIN	A: 3.39	185			
	B: 2.70		141		
	C: 3.52			430	
	D: 2.70				167
	3.00		202		357
	3.50	192	259		864
	4.00	240	338		
	5.00	463	1.03	539	1.55
	6.00	1.08	2.76	2.01	3.25
	7.00	2.35	4.86	4.29	5.69
8.00	4.16	6.95	6.14	10.3	
9.00	6.11	9.11	8.53	13.8	
10.00	8.19	11.7	12.1		
13.00	18.4	27.7	17.8		
16.00	40.1				
DELTA K MAX	A: 16.00	40.1			
	B: 14.67		51.9		
	C: 12.66			58.5	
	D: 8.00				13.8
ROOT MEAN SQUARE		13.51	20.48	18.00	21.76
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73651
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 10.00- 20.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH 64.4 KSI
 ULT STRENGTH 73.7 KSI
 SPECIMEN THK 0.200"
 SPECIMEN WIDTH 1.400"
 REFERENCES: UD002

ALUM. ALLOY
7010

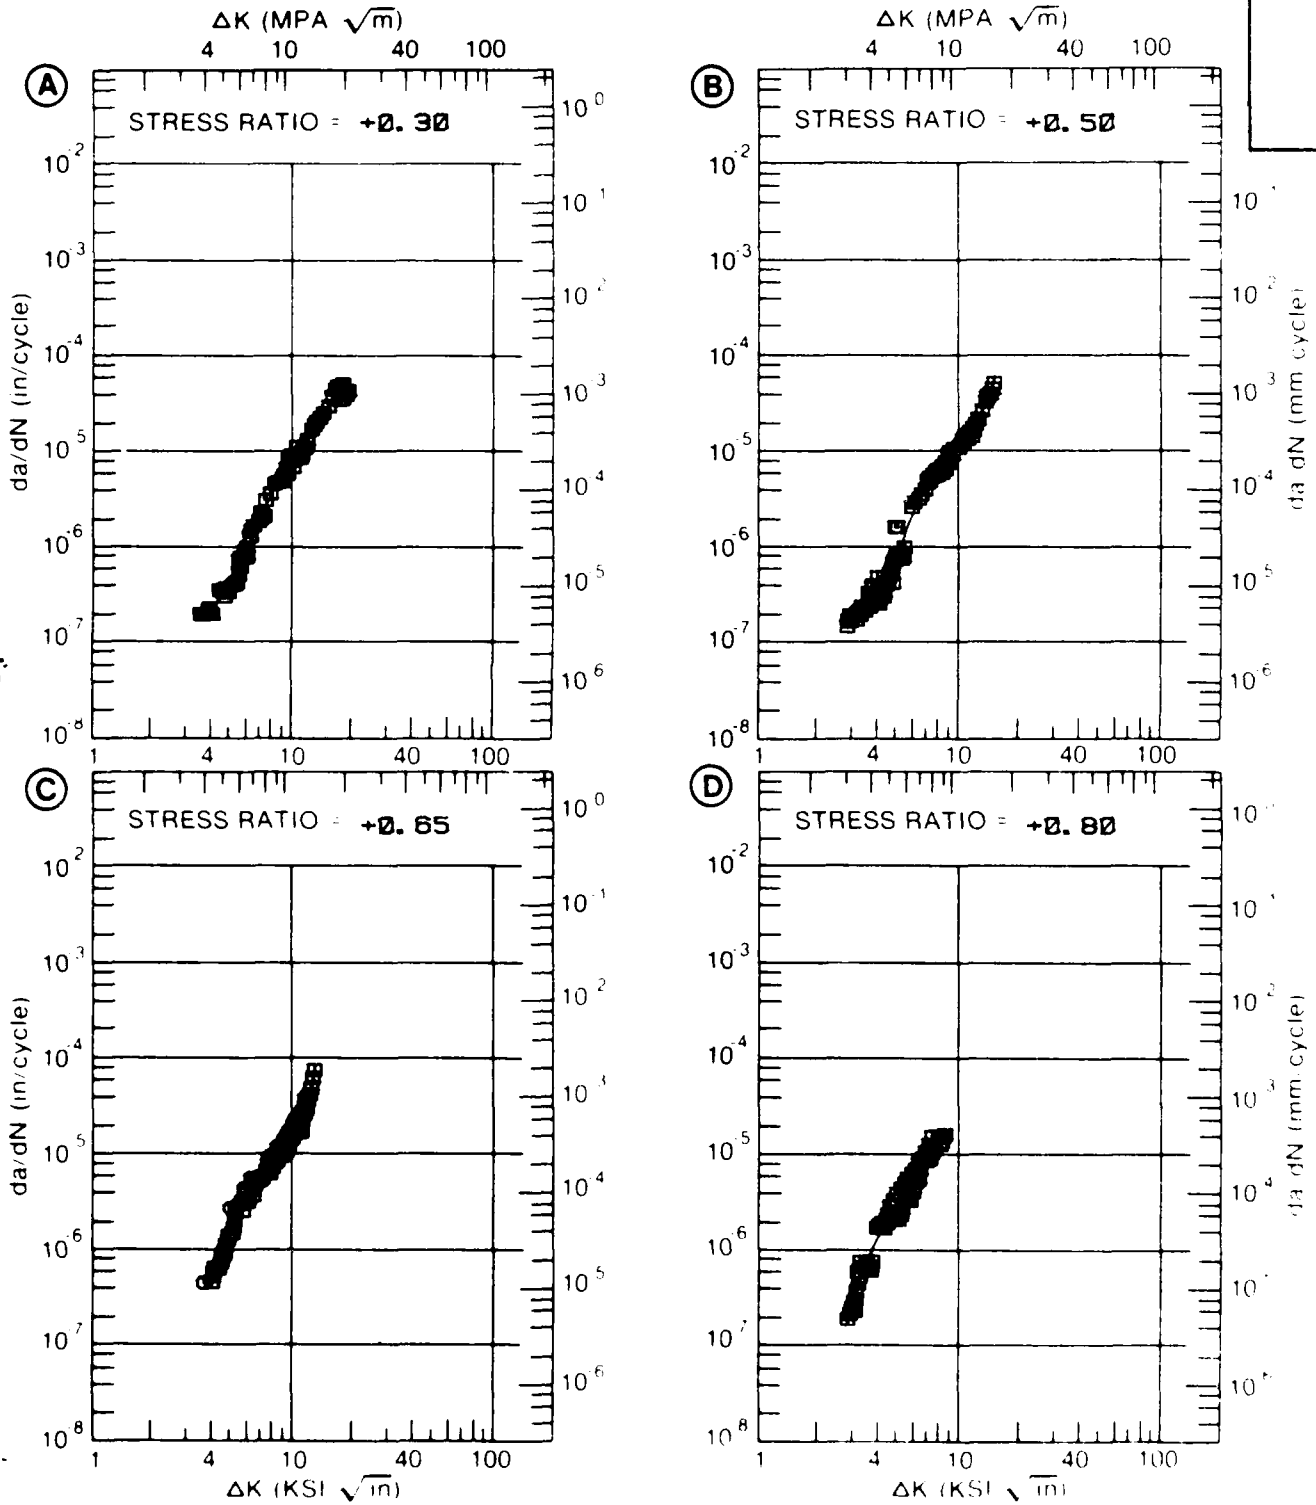


Figure 8.4.3.2

TABLE 8.4.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.4.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7010			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E=+ 250F AIR	E=+ 350F AIR	
DELTA K	A: 4.83	243			
MIN	B: 3.59		.184		
	C: 2.80			.162	
	D:				
	3.00			.301	
	3.50			.449	
	4.00		.531	.725	
	5.00	.250	.943	1.80	
	6.00	.668	2.13	3.60	
	7.00	.998	4.29	6.20	
	8.00	1.33	7.12	9.98	
	9.00	1.91	10.5	15.6	
	10.00	2.83	14.9	24.1	
	13.00	9.07	37.9		
	16.00	23.5			
	20.00	56.5			
DELTA K	A: 23.58	88.6			
MAX	B: 14.35		52.8		
	C: 10.67			32.2	
	D:				
ROOT MEAN SQUARE		19.41	16.45	2.53	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T73651
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 20.00- 25.00 HZ

YIELD STRENGTH: 64.4 KSI
 ULT. STRENGTH: 73.7 KSI
 SPECIMEN THK: 0.300"
 SPECIMEN WIDTH: 1.500"
 REFERENCES: UD002, UD003

ALUM. ALLOY
7010

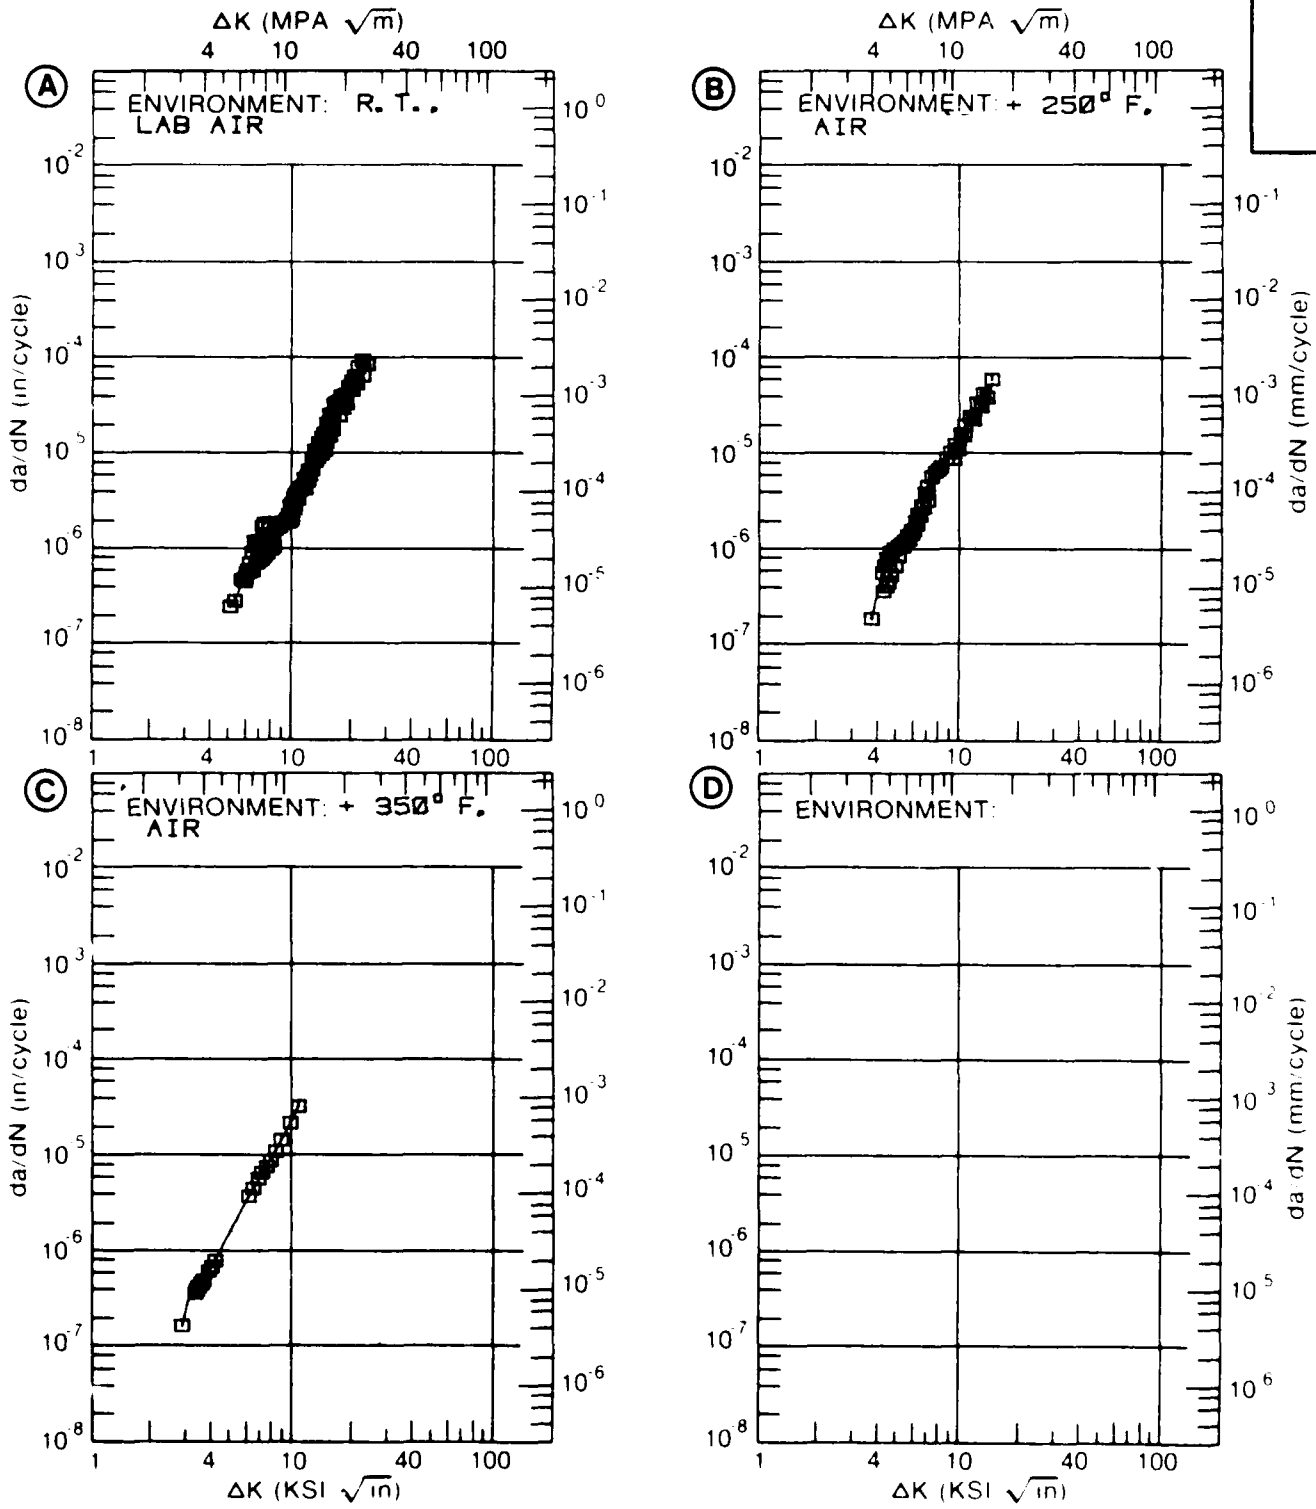


Figure 8.4.3.3

TABLE 8.4.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.4.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7010			
CONDITION: T736S1					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R T	E=+ 250F		
		LAB AIR	AIR		
DELTA K MIN	A: 5.43	.588			
	B: 5.75		3.45		
	C:				
	D:				
	6.00 :	.760	3.99		
	7.00 :	1.69	6.39		
	8.00 :	3.28	9.10		
	9.00 :	4.80	12.2		
	10.00 :	6.03	15.7		
	13.00 :	9.10	31.1		
	16.00 :	13.0			
	20.00 :	22.5			
DELTA K MAX	A: 24.31	46.1			
	B: 15.48		54.5		
	C:				
	D:				
ROOT MEAN SQUARE		9.39	4.95		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	2.0				

CONDITION/HT: T73651
 FORM: 2.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-S
 STRESS RATIO: +0.10
 FREQUENCY: 20.00- 25.00 HZ

YIELD STRENGTH: 62.9 KSI
 ULT. STRENGTH: 73.7 KSI
 SPECIMEN THK: 0.300"
 SPECIMEN WIDTH: 1.500"
 REFERENCES: UD003

ALUM.
ALLOY

7010

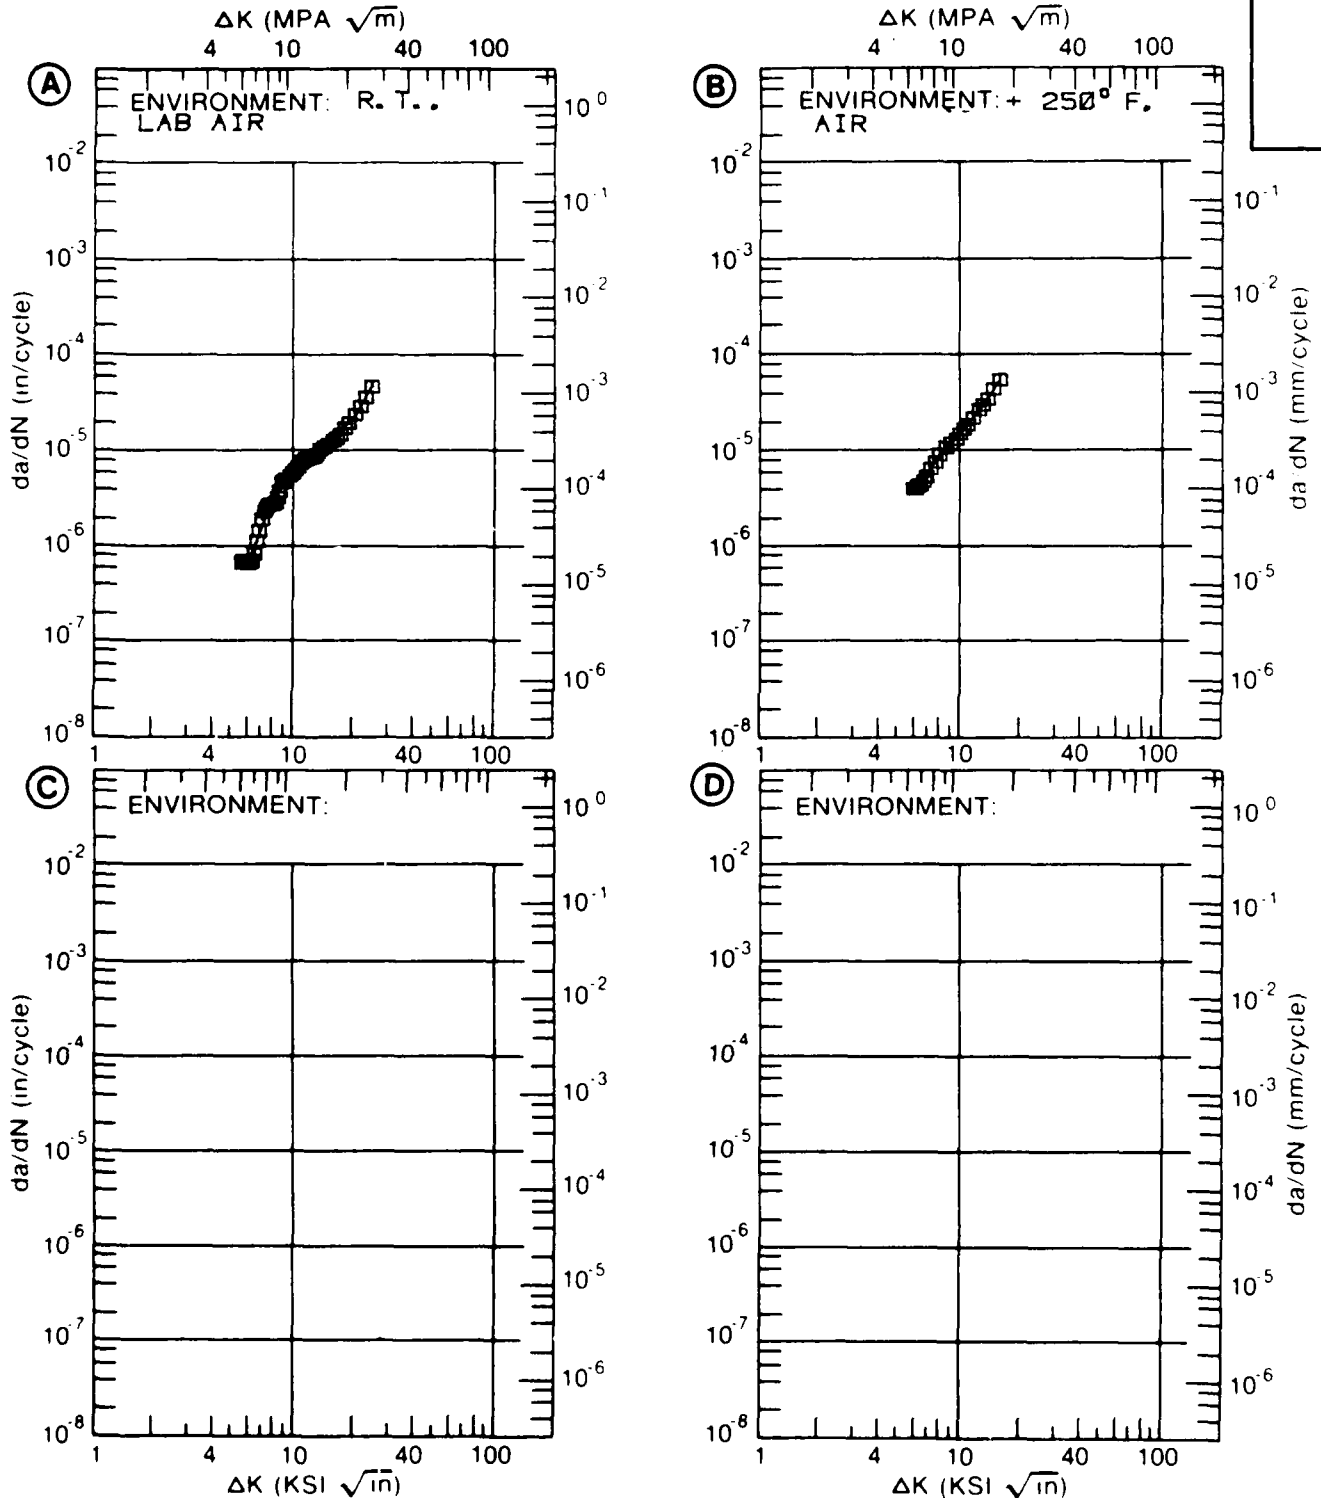


Figure 8.4.3.4

TABLE 8.4.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.4.3.5 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7010			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R.T. LAB AIR	E=+ 250 AIR		
DELTA K	A: 5.31	.420			
MIN	B: 3.83		.259		
	C:				
	D:				
	4.00		.330		
	5.00		1.01		
	6.00	.540	2.24		
	7.00	.831	4.13		
	8.00	1.49	6.81		
	9.00	3.13	10.4		
	10.00	6.15	15.3		
	13.00	15.8	40.7		
	16.00	34.3			
	20.00	85.4			
DELTA K	A: 20.03	85.9			
MAX	B: 14.89		70.6		
	C:				
	D:				
ROOT MEAN SQUARE		15.05	22.86		
PERCENT ERROR					

LIFE 0.0-0.5
 PREDICTION 0.5-0.8
 RATIO 0.8-1.25
 SUMMARY 1.25-2.0
 (NP/NA) >2.0

CONDITION HT T73651
 FORM 2.00" TH PLATE
 SPECIMEN TYPE CT
 ORIENTATION T-L
 STRESS RATIO +0.10
 FREQUENCY 20.00- 25.00 HZ

YIELD STRENGTH: 62.9 KSI
 ULT. STRENGTH: 73.7 KSI
 SPECIMEN THK: 0.300"
 SPECIMEN WIDTH: 1.500"
 REFERENCES: UD003

ALUM.
ALLOY

7010

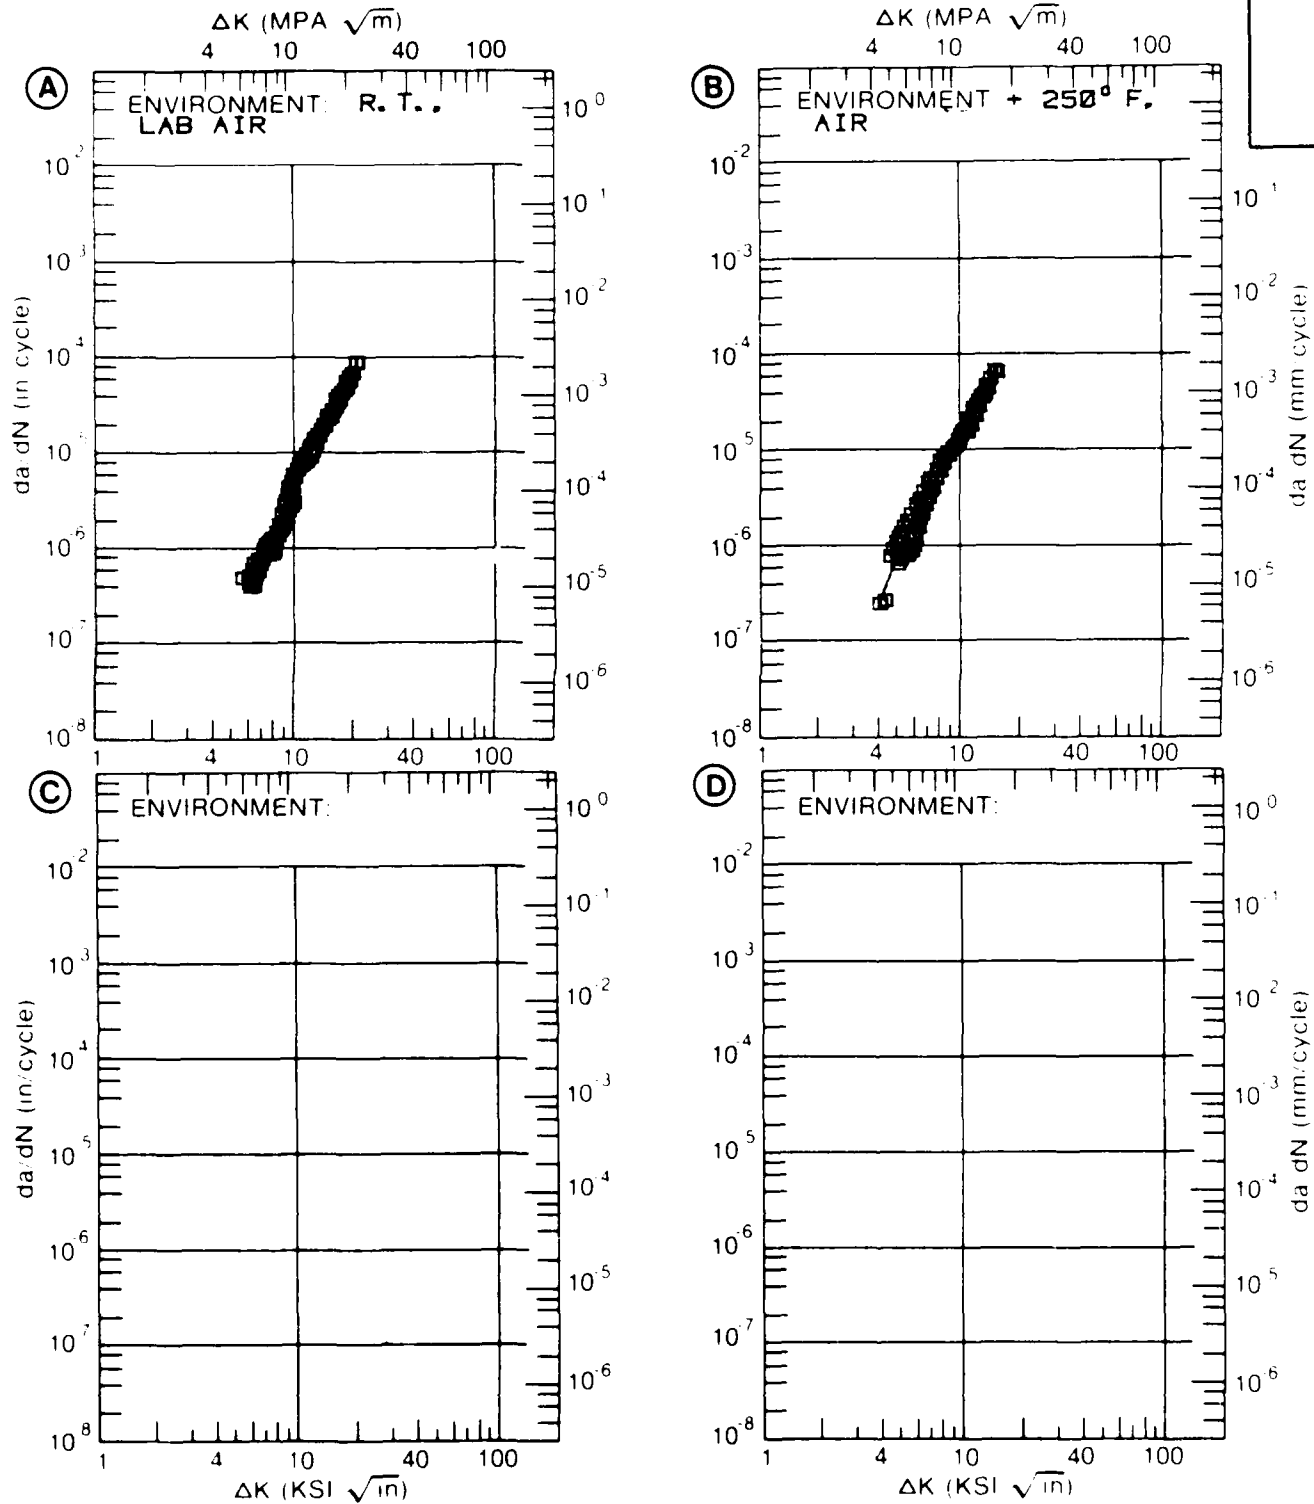


Figure 8.4.3.5

TABLE 8.4.3.6

CONDITION	--PRODUCT--		TEST TEMP OR (F)	SPEC OR (KSI)	YIELD STR (KSI)	ENVIRONMENT	ALUMINUM		K (ISCC)	STAN DEV	MEAN	K (ISCC)	CRACK LENGTH (IN)	K (ISCC)	DATE REFER
	FORM	THICK (IN)					THICK (IN)	WIDTH (IN)							
T73451	P	2 00	R T	T-L	63 2	3 5% NaCl	3 750	1 000	DCB	34 90	30 10	34 90	30 10	59700	1980 BL001
															2 00
T77451	P	2 00	R T	S-L	65 0	3 5% NaCl	1 500	0 750	CT	17 00	32 9/ 3 4	17 00		165720	1980 UF003

TABLE 8.5.3.1

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.5.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7039
CONDITION: T64

K MAX
(KSI*IN**1/2)

DA/DT (10**⁻⁶ IN/HOUR)

A B C D

E=
WET 3X/DAY WITH
3.5% NaCl

K MAX MIN A: 8.00 : 857.
B:
C:
D:

9.00 : 1319.
10.00 : 1834.
13.00 : 3401.
15.00 : 4682.
20.00 : 5828.
25.00 : 6641.
30.00 : 7125.
35.00 : 7506.
40.00 : 7898.

K MAX MAX A: 43.00 : 8165.
B:
C:
D:

ROOT MEAN SQUARE 7.74
PERCENT ERROR

CONDITION/HT: T64
 FORM: 1.0" TH PLATE
 SPECIMEN TYPE: DCB
 ORIENTATION: S-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 CRACK LENGTH (A_0):
 K_{ISCC} :
 REFERENCES: 84284

ALUM. ALLOY
7039

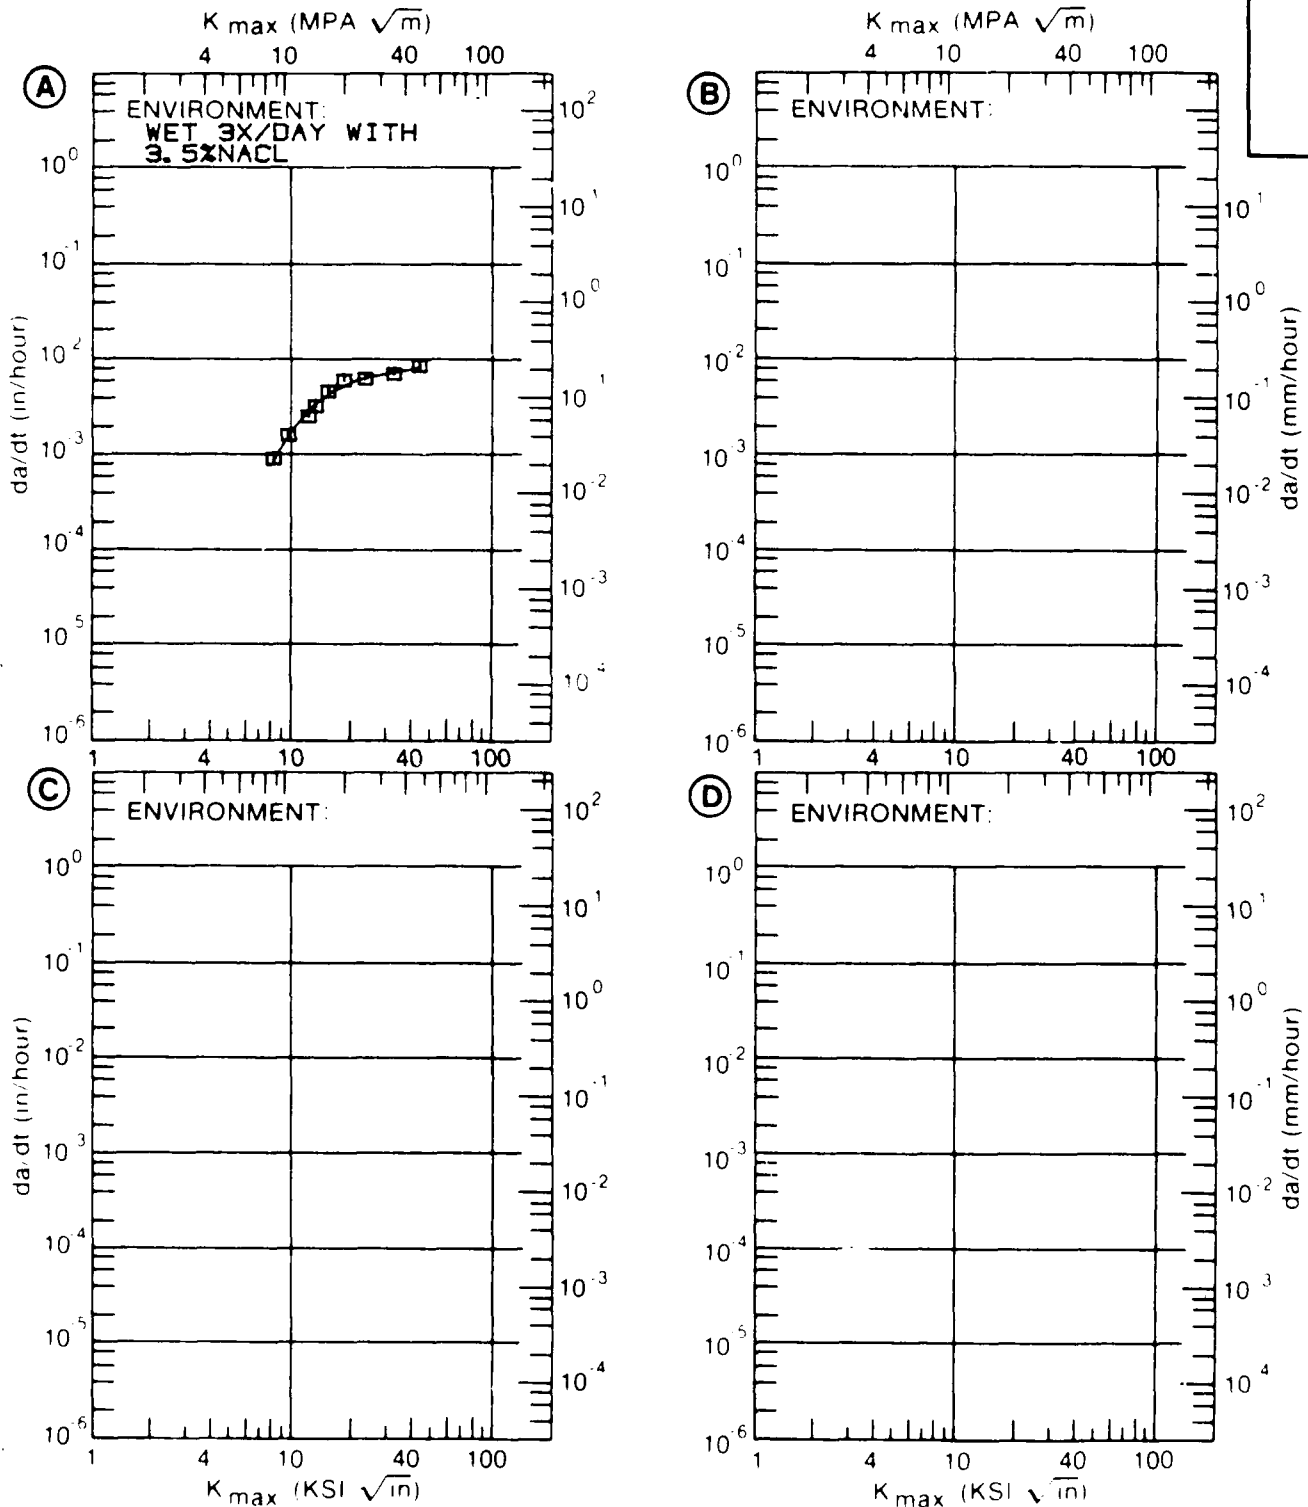


Figure 8.5.3.1

TABLE 8.6.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 7049 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD DEVIATION (NUMBER OF SPECIMENS)	
	(KSI SQRT(IN))	(MPA SQRT(MM))
<u>PLATE</u>		
CONDITION/HT	<u>I-L</u>	<u>S-L</u>
T/351	26.1 ± 1.7 (4)	23.8 ± 0.6 (4)
<u>FORGING</u>		
CONDITION/HT	<u>I-L</u>	<u>S-L</u>
T/3	30.8 ± 3.0 (29)	21.9 ± 2.5 (20)
T/352	38.2 ± 1.0 (2)	19.5 ± 2.8 (6)
<u>EXTRUSION</u>		
CONDITION/HT	<u>I-L</u>	<u>S-L</u>
T/3	28.1 ± 0.7 (3)	25.2 ± 0.5 (3)
<u>EXTRUDED BAR</u>		
CONDITION/HT	<u>I-L</u>	<u>S-L</u>
T/3	31.2 ± 2.7 (3)	22.0 ± 0.5 (3)
T/3511-HIGH PURITY	33.9 ± 0.1 (2)	26.0 ± 0.1 (2)
T/3511 LOW PURITY	27.8 ± 0.3 (2)	18.1 ± 0.1 (2)
T/3511 MEDIUM PURITY	29.7 ± 0.8 (2)	22.1 ± 0.5 (2)
T/6	32.7 ± 1.7 (3)	20.0 ± 0.3 (3)

TABLE 8.6.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 7049

TEST CONDITIONS SPECIMEN ORIENTATION	ENVIRONMENT	L H A A T R T	STRESS RATIO	FREQ (Hz)	PRODUCT FORM	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
						DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50
T7351			1.00	10.00	PLATE			3.59	43.9		
T7351			0.00	10.00	PLATE			2.58	28.3		
T7351			0.50	10.00	PLATE			0.76	14.6	108	
T7351			0.08	6.00	FORGING			4.16	33.1		
T7351			0.08	6.00	FORGING			0.60	5.63		
T7351			0.40	6.00	FORGING		0.06	1.03	11.0		
T7351			0.50	6.00	FORGING		0.11	1.29			

TABLE 8.6.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7049

TEST CONDITIONS

SPECIMEN ORIENTATION	L T	ENVIRONMENT	LAB AIR AT R T	FATIGUE CRACK GROWTH RATES					
				DELTA K LEVELS (KSI SQRT(IN))	2 5	5 10	10 20	20 50	50 100
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)						
T73511-HIGH PURITY	EXTRUSION	0 10	30 00						7 84
T73511-LOW PURITY	EXTRUSION	0 10	30 00						7 32
T73511-MEDIUM PURITY	EXTRUSION	0 10	30 00						3 44

TABLE 8.6.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7049

TEST CONDITIONS

SPECIMEN ORIENTATION

ENVIRONMENT H H A
A T R T

CONDITIONS	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2.5	5	10	20	50	100
773	FORGING	0.33	5.20					15.5		
773511 HIGH PURITY	EXTRUSION	0.10	30.00					15.4		
773511 LOW PURITY	EXTRUSION	0.10	30.00					11.5		
773511 MEDIUM PURITY	EXTRUSION	0.10	30.00					14.2		

TABLE 8.6.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 7049

TEST CONDITIONS

SPECIMEN ORIENTATION | | ENVIRONMENT 3.5% NaCl
AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
T7351	PLATE	0.00	1.00				56.1	224			2157
T7351	PLATE	0.00	10.00				25.1	125			928
T7351	PLATE	1.00	0.10				20.7	96.5			
T7351	PLATE	0.50	0.10			4.30	48.8	228			

TABLE 8.6.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 7049

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT LAB AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
T73511-HIGH PURITY	EXTRUSION	0 10	30 00		7 81
T73511-LOW PURITY	EXTRUSION	0 10	30 00		9 33
T73511-MEDIUM PURITY	EXTRUSION	0 10	30 00		8 36

TABLE 8.6.1.7

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7049

TEST CONDITIONS

REF. ORIENT. T L

ENVIRONMENT SALT FOG AT R I

CONDITION/HT	PREVIOUS FURN	STRESS RATIO	FREQ (HZ)	DELTA K (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)
T 1	FORGING	0.33	18.30	2.5	10
T 2	FORGING	0.33	5.20	5	20
T 3	FORGING	0.33	5.20	2.5	50
T 4	FORGING	0.33	5.20	5	100

TABLE 8.6.2.1

CONDITION	--PRODUCT-- FORM		TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		7049		K(1C)	CRACK LENGTH (IN)	2.5* K(1C)/TVS)**2 (IN)	K(1C)*SORT (IN)	K(1C) STAN MEAN DEV	DATE	REFER	
	THICK (IN)	THICK (IN)				WIDTH (IN)	THICK (IN)	DESIGN	K(1C)								
									A								B
T73	F	2 00	R T	L-S	73.1	1 500	0 750	CT	0 780	0 53	33 60			1972	84368		
T73	F	1 00	B6	L-S	74.9	2 000	0 998	CT	1 059	0 36	28 50			1973	86213		
T73	F	6 00	R T	L-T	55.3	2 000	0 998	CT	1 003	0 64	28 00			1973	86213		
		6 00			55.3	2 000	0 998	CT	0 971	0 54	25 60			1973	86213		
		6 00			58.4	2 000	1 002	CT	0 993	0 90	35 10			1973	86213		
		6 00			58.4	2 000	1 001	CT	1 021	0 76	32 30			1973	86213		
		5 00			60.1	2 000	1 000	CT	1 060	0 52	27 40			1972	84368		
		5 00			60.1	2 000	1 000	CT	1 040	0 47	25 90			1972	84368		
		3 00			65.0	2 000	1 000	CT	1 011	0 56	30 70			1973	86213		
		3 00			65.0	2 000	1 000	CT	1 042	0 67	33 70			1973	86213		
		3 00			65.4	2 000	1 000	CT	1 100	0 57	31 40			1972	84368		
		3 00			65.4	2 000	0 998	CT	1 088	0 54	30 30			1973	86213		
		3 00			65.4	2 000	1 000	CT	1 090	0 54	30 30			1972	84368		
		3 00			65.5	1 500	0 998	CT	1 097	0 58	31 40			1973	86213		
		3 00			65.5	1 500	0 750	CT	0 790	0 69	34 30			1972	84368		
		2 00			65.5	1 500	0 750	CT	0 800	0 64	33 20			1972	84368		
		2 00			67.0	1 000	0 500	CT	0 480	0 46	28 70			1972	84368		
		1 00			67.0	1 000	0 500	CT	0 470	0 45	28 30			1972	84368		
		1 75			67.0	1 000	0 498	CT	0 472	0 45	28 30			1973	86213		
		1 75			67.0	1 000	0 498	CT	0 480	0 46	28 70			1973	86213		
		2 00			68.0	3 500	0 996	CT	1 802	0 43	28 20			1972	84306		
		2 00			68.8	2 000	1 000	CT	1 036	0 42	28 30			1973	86213		
		7 10			70.6	2 000	0 998	CT	1 049	0 40	28 20			1973	86213		
		4 00			72.8	2 000	1 000	CT	1 080	0 55	34 20			1972	84368		
		4 00			72.8	1 990	0 998	CT	1 084	0 55	34 20			1973	86213		
		4 00			72.8	1 990	0 998	CT	1 090	0 47	31 50			1973	86213		
		4 00			72.8	2 000	1 000	CT	1 090	0 47	31 50			1972	84368		
		7 00			73.4	2 000	1 000	CT	1 095	0 58	35 40			1973	86213		
		2 00			74.4	1 000	0 500	CT	0 490	0 43	30 80			1972	84368		
		1 00			74.4	1 000	0 500	CT	0 480	0 42	30 60			1972	84368		
		2 00			75.9	1 500	0 750	CT	0 830	0 60	37 20	30.6/	3 0	1972	84368		
T73	F	5 00	B2	L-T	60.1	2 000	1 000	CT	1 039	0 46	25 90			1973	86213		
		5 00			60.1	2 000	1 000	CT	1 062	0 52	27 40			1973	86213		
		5 00			60.6	1 990	1 000	CT	0 995	0 80	34 30			1973	86213		
		2 70			65.5	1 500	0 747	CT	0 795	0 69	34 30			1973	86213		
		2 70			65.5	1 500	0 747	CT	0 802	0 64	33 20			1973	86213		

TABLE 8.6.2.1 (Con't)

CONDITION	---PRODUCT--- FORM THICK (IN)		TEST SPECIMEN ORIENT (F)	YIELD STRENGTH (KSI)	---SPECIMEN--- WIDTH THICK DESIGN (IN)		CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER	
	M	B			A								
173	F	4 20	82	L-T	65.7	1.500	0.748	CT	0.785	0.49	29 20	1973 86213	
		4 20			65.7	1.500	0.748	CT	0.793	0.49	29 10	1973 86213	
		2 50			68.8	2.000	1.000	CT	1.081	0.29	23 50	1973 86213	
		2 50			73.1	1.500	0.749	CT	0.782	0.53	33 60	1973 86213	
		1 50			74.4	0.990	0.499	CT	0.491	0.43	30 80	1973 86213	
		1 50			74.4	1.000	0.481	CT	0.481	0.42	30 60	1973 86213	
		2 50			75.9	1.500	0.750	CT	0.832	0.60	37 20	30.8/ 4.0	1973 86213
		6 00			59.5	2.000	1.000	CT	1.010	0.66	30 60	1973 86213	
		6 00			59.5	2.000	1.000	CT	1.015	0.79	33 50	32.1/ 2.1	1973 86213
		6 00			55.5	2.000	1.000	CT	0.967	0.29	18 90	1973 86213	
173	F	6 00	R T.	T-L	55.5	2.000	1.000	CT	0.994	0.29	18 80	1973 86213	
		6 00			57.8	2.000	1.001	CT	1.023	0.44	24 20	1973 86213	
		6 00			57.8	2.000	1.002	CT	1.016	0.40	23 00	1973 86213	
		3 00			58.1	2.000	1.000	CT	1.050	0.25	18 40	1972 84368	
		3 00			62.2	2.000	1.000	CT	1.027	0.50	27 90	1973 86213	
		3 00			62.2	2.000	1.000	CT	1.023	0.44	26 20	1973 86213	
		3 00			63.9	2.000	1.000	CT	0.997	0.28	21 20	1973 86213	
		3 00			63.9	2.000	0.999	CT	1.089	0.25	20 40	1973 86213	
		3 00			66.2	2.000	1.000	CT	1.100	0.31	23 40	1972 84368	
		3 00			66.2	1.990	0.998	CT	1.101	0.30	23 40	1973 86213	
173	F	3 00	82	T-L	66.2	2.000	0.998	CT	1.106	0.30	23 00	1973 86213	
		3 00			66.2	2.000	1.000	CT	1.110	0.30	23 00	1972 84368	
		2 00			67.0	2.000	0.999	CT	1.015	0.19	18 70	1973 86213	
		4 00			68.5	2.000	0.998	CT	1.062	0.25	21 70	1973 86213	
		4 00			68.5	2.000	1.000	CT	1.060	0.25	21 70	1972 84368	
		4 00			68.5	2.000	0.998	CT	1.091	0.22	20 20	1973 86213	
		4 00			68.5	2.000	1.000	CT	1.090	0.22	20 20	1972 84368	
		7 10			70.6	2.000	0.999	CT	1.093	0.26	22 60	1973 86213	
		7 00			73.4	2.000	0.998	CT	1.104	0.20	20 70	21.9/ 2.5	1973 86213
		5 00			58.1	2.000	1.000	CT	1.047	0.25	18 40	1973 86213	
173	F	5 00	82	T-L	61.3	1.990	1.000	CT	0.950	0.52	28 00	1973 86213	
		5 00			61.3	1.990	1.000	CT	0.945	0.49	27 10	1973 86213	
		2 00			67.0	2.000	0.999	CT	1.075	0.27	21 90	1973 86213	
		2 00			67.0	2.000	1.000	CT	1.082	0.27	22 00	23.5/ 4.0	1973 86213
6 00	57.6	2.000	1.000	CT	0.988	0.31	20 30	1973 86213					

TABLE 8.6.2.1 (Cont)

CONDITION	--PRODUCT--		YIELD STRENGTH (KSI)	SPECIMEN ORIENT		W	THICKNESS		DESIGN	CRACK LENGTH (IN)		K(1C) (KSI*SQRT IN)	K(1C) MEAN DEV (IN)	K(1C) STAN DEV	DATE	REFER
	FORM	THICK (IN)		TEMP (F)	THICK (IN)		THICK (IN)	A		B						
T73	F	6 00	84	T-L	84	2 000	1 000	CT	1 013	0 36	22 00	21 2/	1 2	1973	86213	
T73	F	6 00	R T	S-L	55 1	2 000	0 999	CT	1 021	0 22	16 30			1973	86213	
		6 00			95 1	2 000	1 000	CT	1 025	0 22	16 20			1973	86213	
		6 00			56 9	2 000	1 000	CT	1 043	0 40	22 70			1973	86213	
		6 00			56 9	2 000	1 000	CT	1 035	0 36	21 70			1973	86213	
		5 00			59 1	2 000	1 000	CT	1 050	0 28	19 70			1972	84368	
		5 00			59 1	2 000	1 000	CT	1 050	0 28	19 80			1972	84368	
		3 00			59 8	2 000	1 001	CT	1 008	0 20	17 10			1973	86213	
		1 00			61 8	1 000	0 500	CT	0 500	0 37	24 00			1972	84368	
		1 00			61 8	1 000	0 500	CT	0 510	0 36	23 70			1972	84368	
		3 00			62 3	2 000	1 000	CT	1 060	0 33	22 70			1972	84368	
		3 00			62 3	2 000	1 000	CT	1 060	0 32	22 30			1972	84368	
		3 00			62 3	2 000	0 996	CT	1 065	0 33	22 70			1973	86213	
		3 00			62 3	2 000	0 998	CT	1 059	0 32	22 30			1973	86213	
		3 00			64 5	2 000	1 000	CT	1 065	0 31	22 80			1973	86213	
		3 00			64 5	2 000	0 999	CT	1 062	0 36	24 60			1973	86213	
		3 00			64 7	1 500	0 750	CT	0 770	0 32	23 00			1972	84368	
		3 00			64 7	1 500	0 750	CT	0 770	0 41	26 20			1972	84368	
		3 00			64 9	1 500	0 750	CT	0 820	0 38	25 40			1972	84368	
		3 00			64 9	1 500	0 750	CT	0 810	0 37	25 10			1972	84368	
		2 00			65 4	2 000	0 999	CT	1 052	0 14	15 60			1973	86213	
		2 00			65 4	2 000	0 998	CT	1 089	0 18	17 60			1973	86213	
		1 75			66 1	1 000	0 498	CT	0 486	0 21	19 10			1973	86213	
		2 00			66 1	1 000	0 500	CT	0 520	0 22	19 60			1972	84368	
		2 00			66 1	1 000	0 500	CT	0 490	0 21	19 10			1972	84368	
		1 75			66 1	1 000	0 498	CT	0 520	0 22	19 60			1973	86213	
		3 00			66 3	1 500	0 750	CT	0 790	0 27	22 40			1972	84368	
		3 00			66 3	1 500	0 750	CT	0 790	0 26	21 80			1972	84368	
		2 00			67 1	1 000	0 500	CT	0 460	0 31	23 50			1972	84368	
		2 00			67 1	1 000	0 500	CT	0 480	0 27	21 90			1972	84368	
		4 00			67 5	2 000	1 000	CT	1 060	0 24	20 80			1972	84368	
		4 00			67 5	2 000	1 000	CT	1 050	0 24	20 70			1972	84368	
		4 00			67 5	2 000	0 998	CT	1 058	0 24	20 80			1973	86213	
		4 00			67 5	2 000	0 998	CT	1 054	0 24	20 70			1973	86213	
		1 00			67 6	1 500	0 750	CT	0 800	0 29	23 10			1972	84368	
		2 00			67 6	1 500	0 750	CT	0 800	0 30	23 40			1972	84368	
		---			68 9	1 000	0 500	CT	0 500	0 22	20 50			1972	83242	
		---			68 9	1 000	0 500	CT	0 500	0 22	20 50			1972	83242	

TABLE 8.6.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	SPECKLE			CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) (KSI*SQRT IN)	K(1C) MEAN (IN)	STAN DEV	DATE	REFER		
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)	DESIGN								A	
																W	B
173	F		68.9	R T	S-L	1.000	0.500	CT	0.500	0.24	21.20	21.30	2.5	1972	83242		
			68.9			1.000	0.500	CT	0.500	0.24	21.20	21.30		1972	83242		
173	F	5.00	59.1	82	S-L	2.000	1.000	CT	1.051	0.28	19.60			1973	86213		
		5.00	59.1			2.000	1.000	CT	1.048	0.28	19.70			1973	86213		
		5.00	60.1			1.990	1.000	CT	0.956	0.23	18.20			1973	86213		
		5.00	60.1			1.990	1.000	CT	0.980	0.22	17.90			1973	86213		
		1.00	62.6			1.000	0.501	CT	0.513	0.36	23.70			1973	86213		
		1.00	62.6			1.000	0.499	CT	0.499	0.37	24.00			1973	86213		
		2.70	64.7			1.500	0.748	CT	0.774	0.32	23.00			1973	86213		
		2.70	64.7			1.500	0.748	CT	0.773	0.41	26.20			1973	86213		
		2.50	64.9			1.500	0.748	CT	0.820	0.38	25.40			1973	86213		
		2.50	64.9			1.500	0.748	CT	0.813	0.37	25.10			1973	86213		
		2.00	65.4			1.620	0.751	CT	0.779	0.13	15.00			1973	86213		
		1.50	67.1			0.990	0.499	CT	0.464	0.31	23.50			1973	86213		
		1.50	67.1			0.990	0.498	CT	0.480	0.27	21.90			1973	86213		
		1.50	67.6			1.500	0.750	CT	0.799	0.30	23.40			1973	86213		
		1.50	67.6			1.500	0.750	CT	0.798	0.29	23.10			1973	86213		
		2.50	67.8			1.500	0.749	CT	0.789	0.27	22.40			1973	86213		
		2.50	67.8			1.500	0.751	CT	0.794	0.26	21.60			1973	86213		
		4.20	69.7			1.500	0.747	CT	0.782	0.17	18.40			1973	86213		
		4.20	69.7			1.500	0.748	CT	0.794	0.18	18.70	21.60	3.0	1973	86213		
173	F	6.00	58.7	84	S-L	2.000	1.000	CT	1.028	0.28	19.60			1973	86213		
		6.00	58.7			2.000	1.000	CT	1.024	0.28	19.70			1973	86213		
		0.75	68.2			1.000	0.500	CT	0.515	0.29	23.20			1973	86213		
		0.75	68.2			1.000	0.500	CT	0.516	0.30	23.60			1973	86213		
		0.75	71.5			1.000	0.475	CT	0.535	0.22	21.30			1973	86213		
		0.75	71.5			1.000	0.494	CT	0.539	0.25	22.60	21.70	1.7	1973	86213		
173	E	3.00	78.9	65	L-T	2.000	1.000	CT	1.000	0.22	23.60			1972	83061		
		3.00	78.9			2.000	1.000	CT	1.000	0.26	25.40			1972	83061		
		3.00	78.9			2.000	1.000	CT	1.000	0.26	25.20	24.70	1.0	1972	83061		
173	F	3.00	76.8	0	L-T	2.000	1.000	CT	1.000	0.25	24.50			1972	83061		
		3.00	76.8			2.000	1.000	CT	1.000	0.30	26.80			1972	83061		
		3.00	76.8			2.000	1.000	CT	1.000	0.29	26.30	25.90	1.2	1972	83061		
173	F	3.00	74.8	R T	L-T	2.000	1.000	CT	1.000	0.33	27.30			1972	H3041		

TABLE 8.6.2.1 (Con't)

CONDITION	ALUMINUM										K(1C)	K(1C) STAN MEAN DEV (KSI*SQRT IN)	DATE	REFER		
	--PRODUCT--		TEST SPECIMEN		SPECIMEN		CRACK		2.5*							
	FORM	THICK (IN)	TEMP (F)	ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	LENGTH (IN)	(K(1C)/TYS)**2 (IN)					(K(1C)*SQRT IN)	
173	F	3 00	R T	L-T	74 8	2 000	1 000	CT	1 000	0 36	28 60	28 60	28 1/	0 7	1972	83061
		3 00			74 8	2 000	1 000	CT	1 000	0 36	28 30	28 30	28 1/	0 7	1972	83061
173	E	3 00	-	65	T-L	77 5	2 000	1 000	CT	0 22	22 80	23 70	23 3/	0 6	1972	83061
		3 00			77 5	2 000	1 000	CT	1 000	0 22	23 70	23 70	23 3/	0 6	1972	83061
173	E	3 00	0	T-L	76 3	2 000	1 000	CT	1 000	0 24	23 80	23 80	24 1/	0 7	1972	83061
		3 00			76 3	2 000	1 000	CT	1 000	0 27	24 90	24 90	24 1/	0 7	1972	83061
		3 00			76 3	2 000	1 000	CT	1 000	0 24	23 60	23 60	24 1/	0 7	1972	83061
173	E	3 00	R T	T-L	75 0	2 000	1 000	CT	1 000	0 29	25 70	25 70	25 2/	0 5	1972	83061
		3 00			75 0	2 000	1 000	CT	1 000	0 28	25 30	25 30	25 2/	0 5	1972	83061
		3 00			75 0	2 000	1 000	CT	1 000	0 27	24 70	24 70	25 2/	0 5	1972	83061
173	E	3 00	-	65	S-T	72 7	---	---	---	0 21	21 10	21 10	22 2/	1 6	1972	83061
		3 00			72 7	---	---	---	---	0 26	23 30	23 30	22 2/	1 6	1972	83061
173	F	3 00	0	S-T	71 2	---	---	---	---	0 25	22 50	19 80	21 2/	1 9	1972	83061
		3 00			71 2	---	---	---	---	0 19	22 50	19 80	21 2/	1 9	1972	83061
173	F	3 00	R T	S-T	68 6	---	---	---	---	0 21	20 10	20 10	20 3/	0 2	1972	83061
		3 00			68 6	---	---	---	---	0 22	20 50	20 50	20 3/	0 2	1972	83061
		3 00			68 6	---	---	---	---	0 22	20 30	20 30	20 3/	0 2	1972	83061
173	FB	3 50	-	65	L-T	71 7	2 000	1 000	CT	0 52	32 60	32 60	31 4/	1 7	1972	83061
		3 50			71 7	2 000	1 000	CT	1 000	0 42	29 40	29 40	31 4/	1 7	1972	83061
		3 50			71 7	2 000	1 000	CT	1 000	0 51	32 20	32 20	31 4/	1 7	1972	83061
173	EB	3 50	0	L-T	77 3	2 000	1 000	CT	1 000	0 50	34 70	34 70	34 2/	0 5	1972	83061
		3 50			77 3	2 000	1 000	CT	1 000	0 48	33 80	33 80	34 2/	0 5	1972	83061
		3 50			77 3	2 000	1 000	CT	1 000	0 49	34 20	34 20	34 2/	0 5	1972	83061
173	EB	3 25	R T	L-T	73 4	2 000	1 000	CT	1 000	0 55	34 40	34 40	33 2/	2 7	1972	83061
		3 50			73 4	2 000	1 000	CT	1 000	0 42	30 10	30 10	33 2/	2 7	1972	83061
		3 50			73 4	2 000	1 000	CT	1 000	0 57	35 10	35 10	33 2/	2 7	1972	83061
173	FR	3 50	-	65	T-L	70 3	2 000	1 000	CT	0 18	18 90	18 90	20 0/	1 0	1972	83061
		3 50			70 3	2 000	1 000	CT	1 000	0 22	20 80	20 80	20 0/	1 0	1972	83061
		3 50			70 3	2 000	1 000	CT	1 000	0 21	20 20	20 20	20 0/	1 0	1972	83061

TABLE 8.6.2.1 (Con't)

CONDITION	ALUMINUM		YIELD (KSI)	SPECIMEN THICK (IN)	DESIGN (IN)	CRACK LENGTH (IN)	2.5* (IN)	K(1C)/TYS)**2	K(1C) MEAN DEV (KSI*SQRT IN)	STAM DEV	DATE	REFER
	FORM	THICK (IN)										
T73	EB	3 50	0	T-L	1 000	CT	1 000	0.22	20 60		1972	83061
		3 50			2 000	CT	1 000	0.22	20 40		1972	83061
		3 50			2 000	CT	1 000	0.23	20 90	20.6/	0.3	1972
T73	EB	3 50	R T	T-L	1 000	CT	1 000	0.25	21 50		1972	83061
		3 50			2 000	CT	1 000	0.27	22 40		1972	83061
		3 50			2 000	CT	1 000	0.27	22 10	22.0/	0.5	1972
T73	EB	3 50	-	65	S-T	1 000	CT	1 000	0.24		1972	83061
T73	EB	3 50	0	S-T	1 000	CT	1 000	0.27	21 80		1972	83061
		3 50			2 000	CT	1 000	0.25	21 00		1972	83061
		3 50			2 000	CT	1 000	0.26	21 60	21.5/	0.4	1972
T73	EB	3 50	R T	S-T	1 000	CT	1 000	0.30	22 50		1972	83061
		3 50			2 000	CT	1 000	0.30	22 60		1972	83061
		3 50			2 000	CT	1 000	0.33	23 80	23.0/	0.7	1972
T7351	P	4 00	R T	T-L	1 500	CT	0.722	0.51	24 10		1973	86213
		4 00			1 490	CT	0.725	0.56	25 40		1973	86213
		2 00			1 500	CT	0.750	0.52	27 20		1973	86213
		2 00			1 500	CT	0.751	0.55	27 80	26.1/	1.7	1973
T7351	P	4 00	R T	S-L	1 490	CT	0.700	0.53	23 20		1973	86213
		4 00			1 500	CT	0.730	0.59	24 00		1973	86213
		2 00			1 490	CT	0.715	0.42	23 50		1973	86213
		2 00			1 490	CT	0.704	0.45	24 50	23.8/	0.6	1973
T73511-HIGH/ PURITY	EB	1 50	R T	L-T	2 500	CT	-----	0.49	34 00		1980	WA001
		1 50			2 500	CT	-----	0.49	33 80	33.9/	0.1	1980
T73511-HIGH/ PURITY	EB	1 50	R T	T-L	2 500	CT	-----	0.34	26 00		1980	WA001
		1 50			2 500	CT	-----	0.34	25 90	26.0/	0.1	1980

TABLE 8.6.2.1 (Con't)

CORRELATION	ALUMINUM		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	SPECIMEN		CRACK LENGTH (IN)	2.5* K(KIC)/TYS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)			WIDTH (IN)	THICK (IN)						
T73511 LOW PURITY	EB	1.50	R T	73.1	2.500	1.250	CT	0.27	24.00	0.3	1980	WA001
		1.50		73.1	2.500	1.250	CT	0.26	23.60	0.3	1980	WA001
T73511 LOW PURITY	EB	1.50	R T	68.6	2.500	1.250	CT	0.18	18.20	0.1	1980	WA001
		1.50		68.6	2.500	1.250	CT	0.17	18.00	0.1	1980	WA001
T73511-MEDIUM PURITY	EB	1.50	R T	75.4	2.500	1.250	CT	0.40	30.30	0.8	1980	WA001
		1.50		75.4	2.500	1.250	CT	0.37	29.10	0.8	1980	WA001
T73511-MEDIUM PURITY	EB	1.50	R T	69.2	2.500	1.250	CT	0.25	21.70	0.9	1980	WA001
		1.50		69.2	2.500	1.250	CT	0.26	22.40	0.9	1980	WA001
T7352	F	7.10	R T	65.0	3.990	1.998	CT	1.882	37.50	1.0	1973	85836
		7.10		65.0	3.990	1.997	CT	1.900	38.90	1.0	1973	85836
T7342	F	6.00	R T	50.5	2.000	0.999	CT	0.931	19.10		1973	86213
		6.00		50.5	2.000	0.999	CT	0.954	15.80		1973	86213
		3.00		58.6	2.000	0.999	CT	1.003	17.30		1973	86213
		7.10		62.0	2.500	1.252	CT	1.292	23.40		1973	85836
		3.00		63.8	2.000	1.000	CT	1.045	21.90		1973	86213
	3.00		63.8	2.000	1.000	CT	1.039	19.70	2.8		1973	86213
T74	EB	3.50	-	80.0	2.000	1.000	CT	1.000	30.30		1972	83061
		3.50	65	80.0	2.000	1.000	CT	1.000	30.30		1972	83061
		3.50		80.0	2.000	1.000	CT	1.000	30.50	0.1	1972	83061
T76	EB	3.50	0	77.1	2.000	1.000	CT	1.000	34.10		1972	83061
		3.50		77.1	2.000	1.000	CT	1.000	32.30		1972	83061
		3.50		77.1	2.000	1.000	CT	1.000	32.90	0.9	1972	83061
T75	EB	3.25	R T	75.5	2.000	1.000	CT	1.000	34.20		1972	83061
		3.50		75.5	2.000	1.000	CT	1.000	30.60		1972	83061
		3.50		75.5	2.000	1.000	CT	1.000	33.10	1.7	1972	83061

TABLE 8.6.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	SPECIMEN		DESIGN LENGTH (IN)	CRACK LENGTH (IN)	2.5* (K(IC)/TYS)**2 (IN)	K(IC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER	
	FORM	THICK (IN)				THICK (IN)	WIDTH (IN)								
176	EB	3 50	72.9	T-L	69	2 000	1 000	CT	1 000	0 17	19 00		1972	83061	
		3 50	72.9			2 000	1 000	CT	1 000	0 18	19 30	19 2/	0 2	1972	83061
176	EB	3 50	70.6	T-L	0	2 000	1 000	CT	1 000	0 22	20 80		0 8	1972	83061
		3 50	70.6			2 000	1 000	CT	1 000	0 19	19 60	20 2/	0 8	1972	83061
176	EP	3 50	68.6	T-L	R T	2 000	1 000	CT	1 000	0 22	20 30			1972	83061
		3 50	68.6			2 000	1 000	CT	1 000	0 21	19 70		0 3	1972	83061
		3 50	68.6			2 000	1 000	CT	1 000	0 21	20 00	20 0/	0 3	1972	83061
176	EB	3 50	67.5	S-T	65	2 000	1 000	CT	1 000	0 22	19 90			1972	83061
		3 50	67.5			2 000	1 000	CT	1 000	0 21	19 10			1972	83061
		3 50	67.5			2 000	1 000	CT	1 000	0 21	19 30	19 4/	0 4	1972	83061
176	EB	3 50	66.6	S-T	0	2 000	1 000	CT	1 000	0 25	21 20			1972	83061
		3 50	66.6			2 000	1 000	CT	1 000	0 24	20 70			1972	83061
		3 50	66.6			2 000	1 000	CT	1 000	0 24	20 50	20 8/	0 4	1972	83061
176	EB	3 50	65.8	S-T	R T	2 000	1 000	CT	1 000	0 25	20 90			1972	83061

TABLE 8.6.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049
CONDITION: T73

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 6.17	4.17			
	B: 6.21		10.4		
	C: 6.07			9.11	
	D: 7.00				
	7.00	6.89	11.7	10.8	
	8.00	10.1	16.5	15.7	
	9.00	14.8	30.7	21.5	
	10.00	24.8	28.5	30.1	
DELTA K MAX	A: 11.88	112.			
	B: 10.89		100.		
	C: 11.44			76.4	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		16.76	9.08	7.82	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	1	1	

CONDITION/HT: T73
 FORM: 4.00- 5.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30

YIELD STRENGTH: 58.1- 68.5 KSI
 ULT. STRENGTH: 68.4- 76.4 KSI
 SPECIMEN THK: 1.495- 1.502"
 SPECIMEN WIDTH: 3.800"
 REFERENCES: 86842

ALUM.
ALLOY

7049

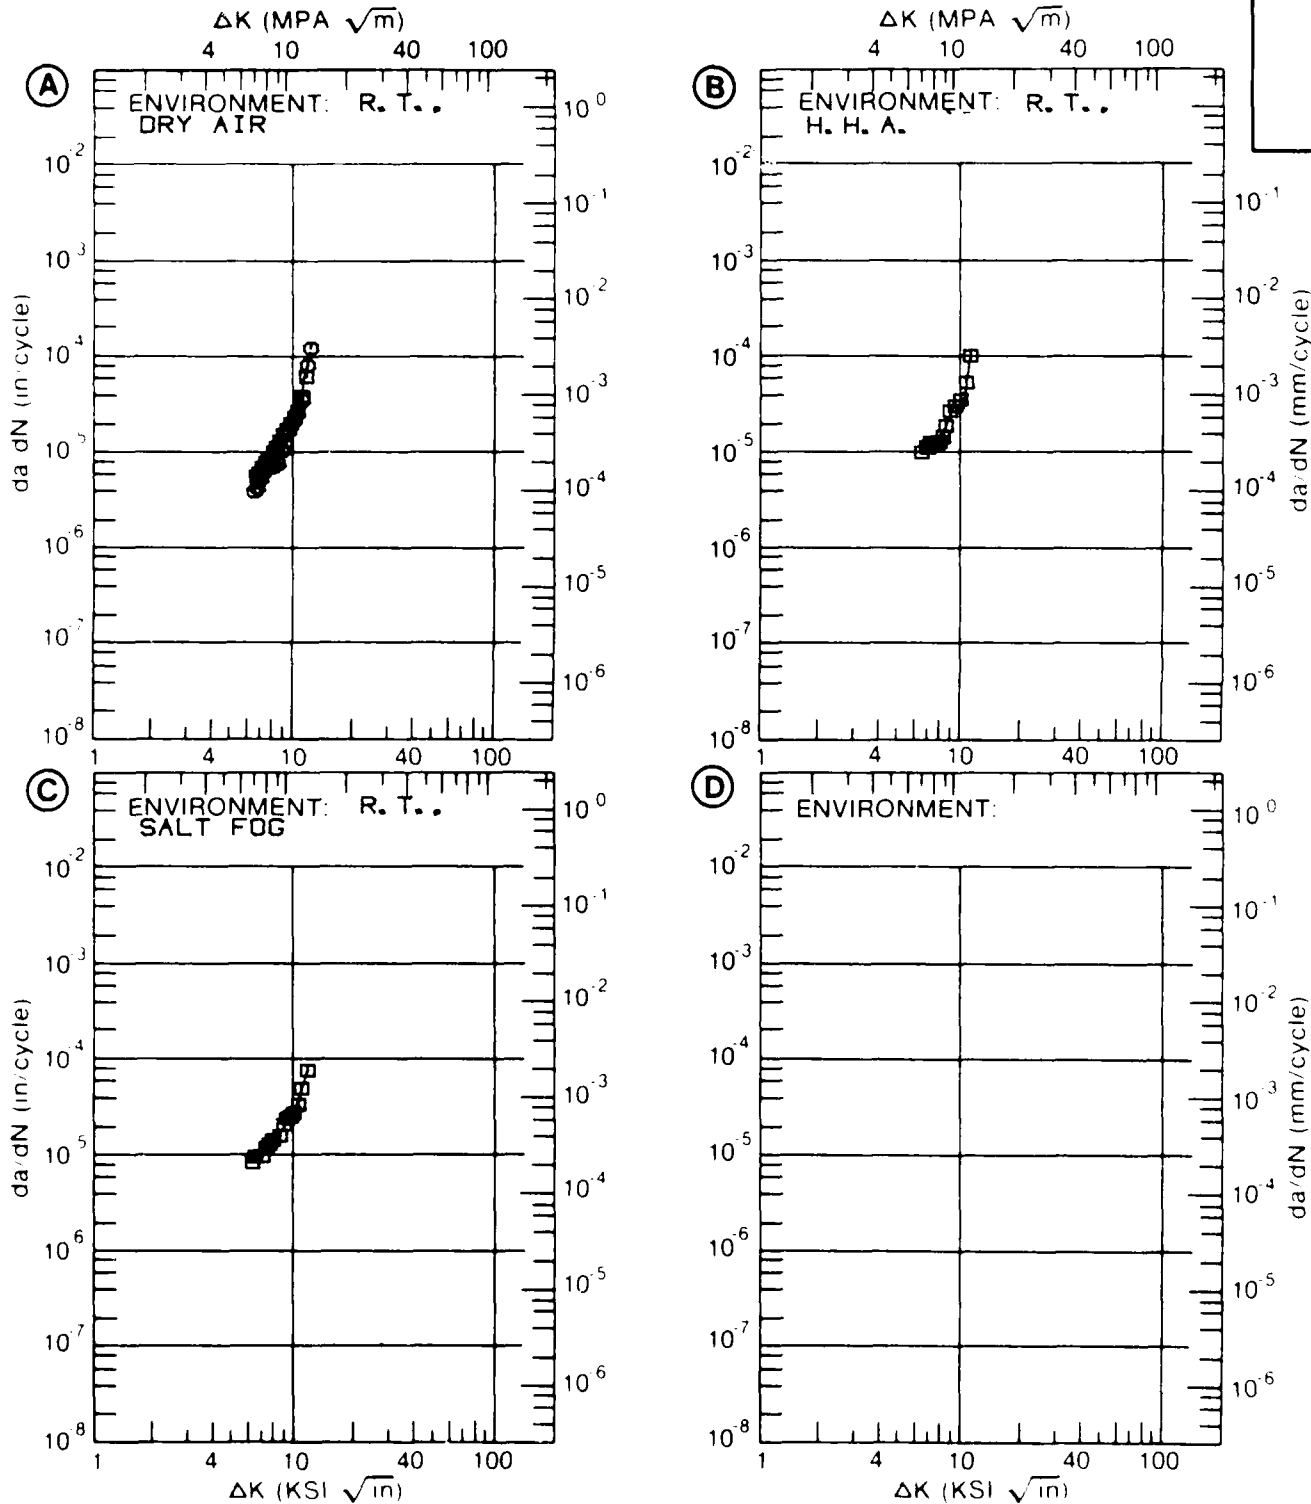


Figure 8.6.3.1

TABLE 8.6.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049
CONDITION: T73

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.98 B: 6.02 C: 5.30 D:	2.16	3.75	3.18
	6.00 7.00 8.00 9.00 10.00 13.00 16.00 20.00	2.21 3.98 6.87 10.3 13.9 28.6 62.3	6.87 10.0 12.5 15.5 42.9	5.58 9.92 14.0 17.9 22.2 46.1 105. 130.
DELTA K MAX	A: 17.34 B: 15.15 C: 20.25 D:	82.1	71.3	126.
ROOT MEAN SQUARE PERCENT ERROR	5.13	6.07	6.24	

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1
---------------------------------------	--	---	---	---

CONDITION/HT: T73
 FORM: 5.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 5.20

YIELD STRENGTH: 60.1 KSI
 ULT. STRENGTH: 70.3 KSI
 SPECIMEN THK: 0.748- 0.750"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 86842

ALUM.
ALLOY

7049

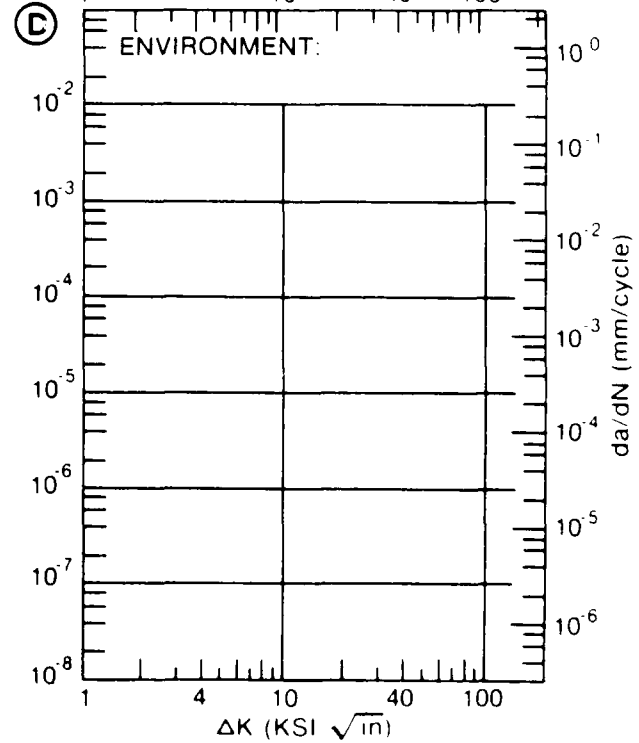
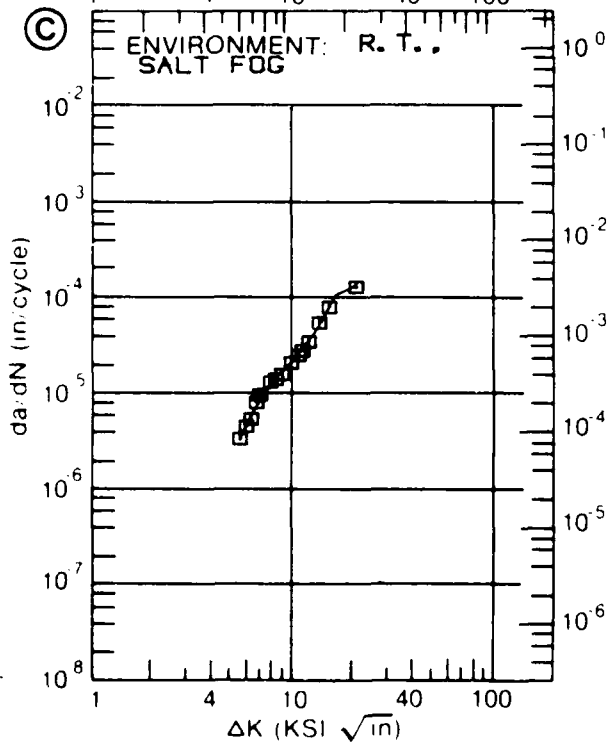
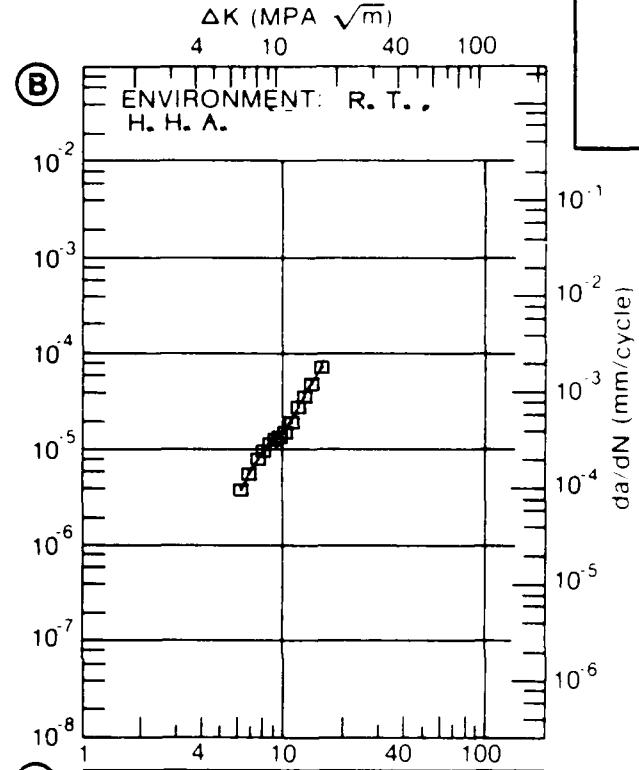
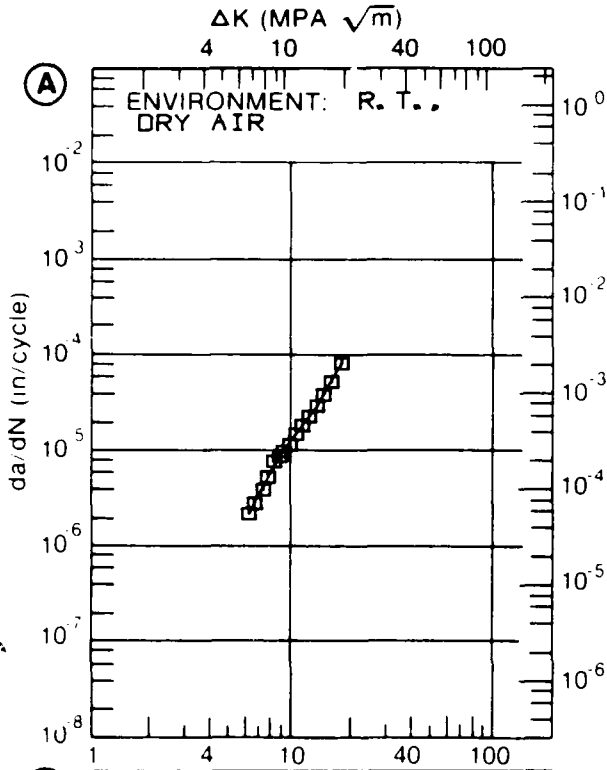


Figure 8.6.3.2

TABLE 8.6.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049
CONDITION: T73

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
E= R. T. SALT FOG				
DELTA K MIN	A: 5.98	B: 6.46		
	6.00	6.57		
	7.00	12.2		
	8.00	18.3		
	9.00	25.3		
	10.00	34.3		
DELTA K MAX	A: 12.94	B: 99.5		

ROOT MEAN SQUARE PERCENT ERROR 14.86

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	1
	0.5-0.8	2
	0.8-1.25	
	1.25-2.0	
	>2.0	

CONDITION: HT T73
 FORM: 5.00" TH FORGING
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 5.20

YIELD STRENGTH: 58.1 KSI
 ULT STRENGTH: 68.4 KSI
 SPECIMEN THK: 0.745-0.752"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 86842

A. 25
 A. 107

7249

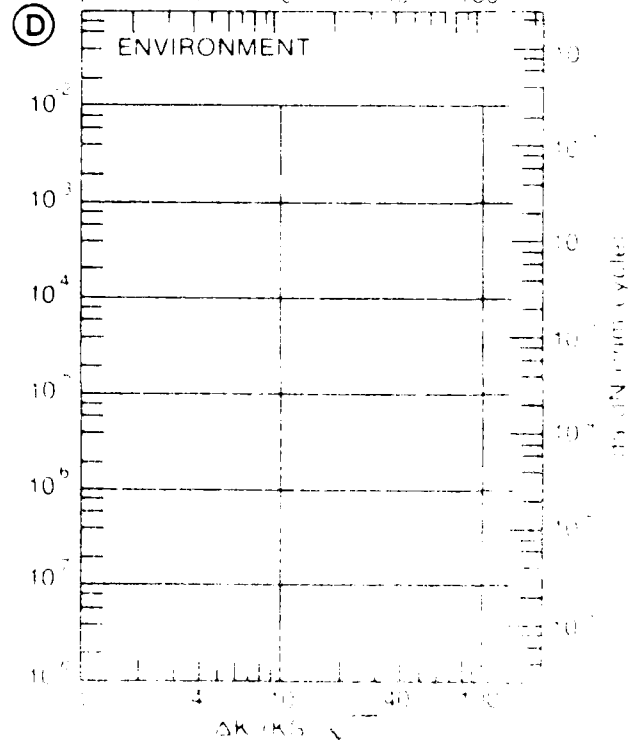
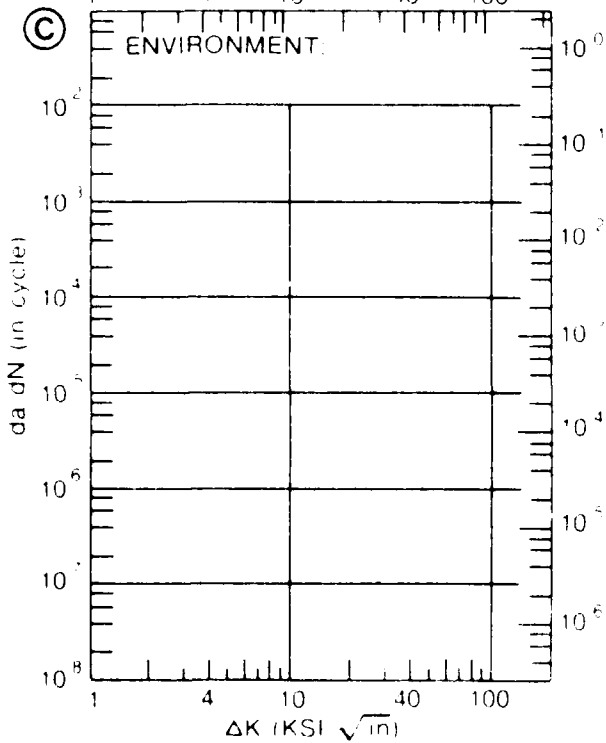
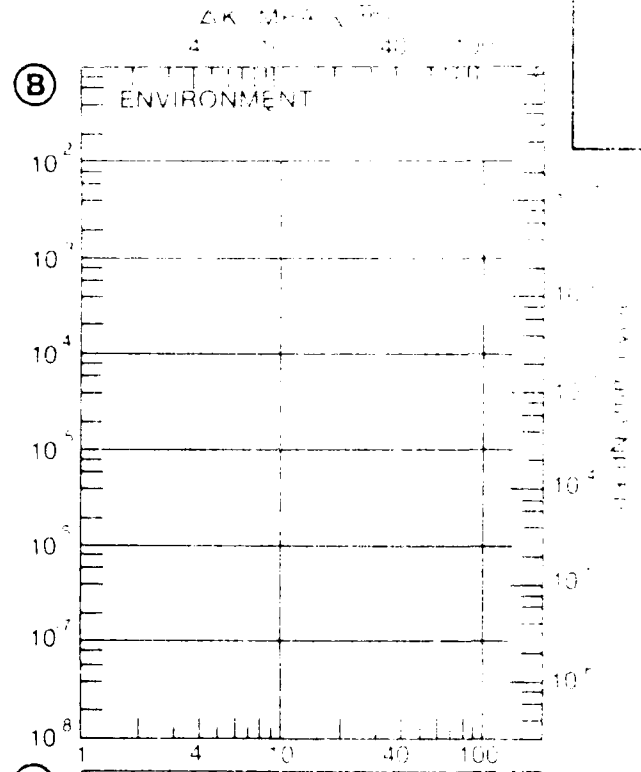
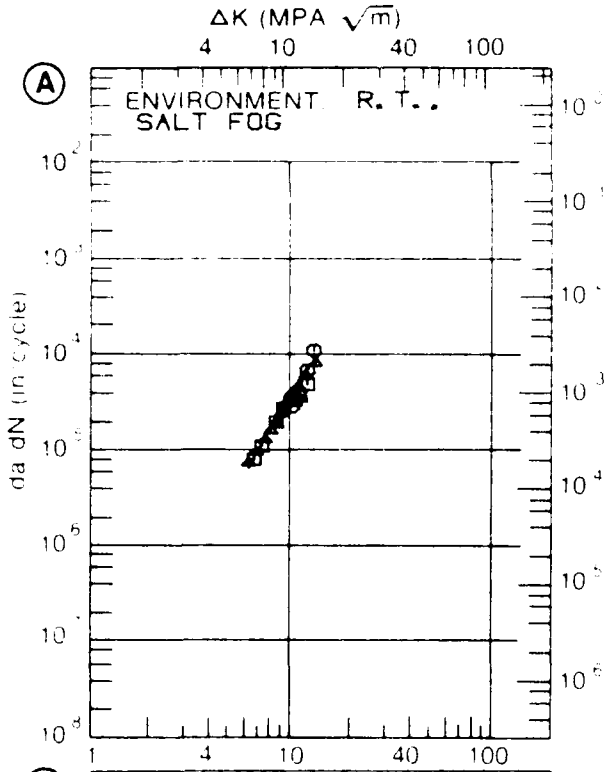


Figure 8.1.3.1

TABLE 8.6.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7049			
CONDITION: T/3					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A		
DELTA K MIN	A: 6.20	.211			
	B: 6.14		1.80		
	C:				
	D:				
	7.00	.883	4.42		
	8.00	1.66	10.0		
	9.00	2.60	14.7		
	10.00	6.08	18.7		
	13.00	18.0			
DELTA K MAX	A: 13.74	31.7			
	B: 11.75		41.3		
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		16.39	16.49		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1		

CONDITION/HT: T73
 FORM: 5.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: S-T
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 59.1 KSI
 ULT. STRENGTH: 68.1 KSI
 SPECIMEN THK: 1.500- 1.501"
 SPECIMEN WIDTH: 3.800"
 REFERENCES: 86842

ALUM. ALLOY
7049

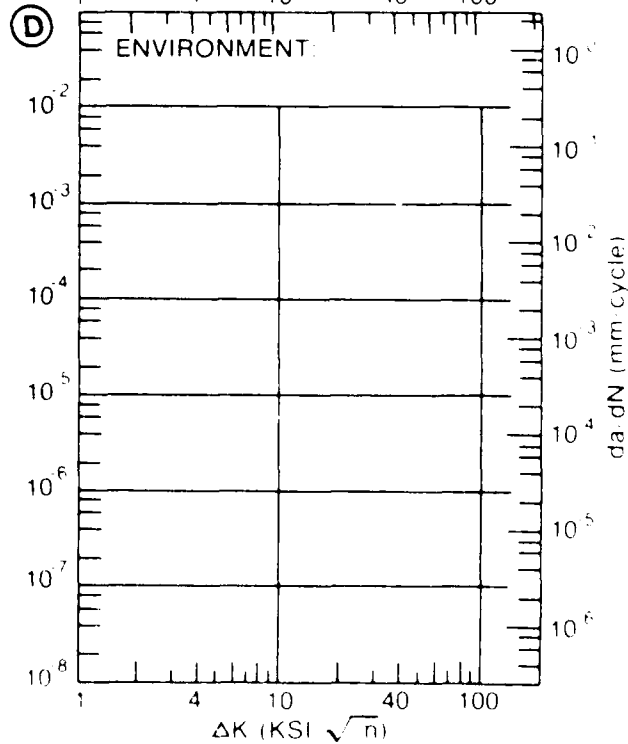
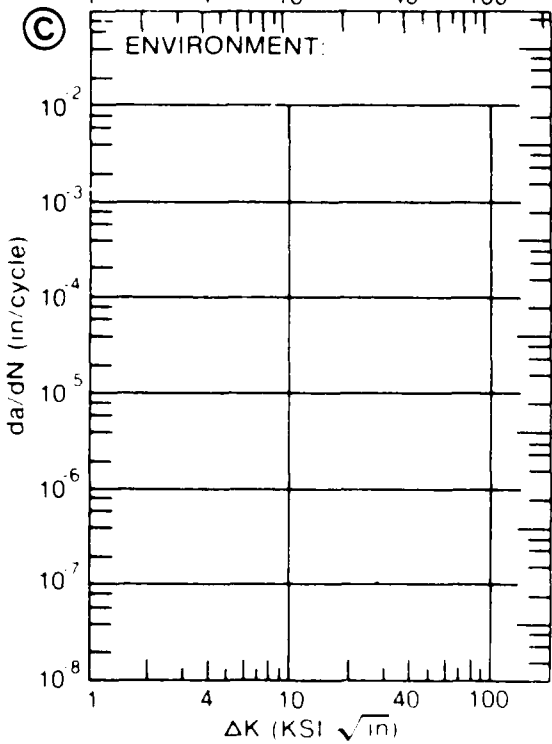
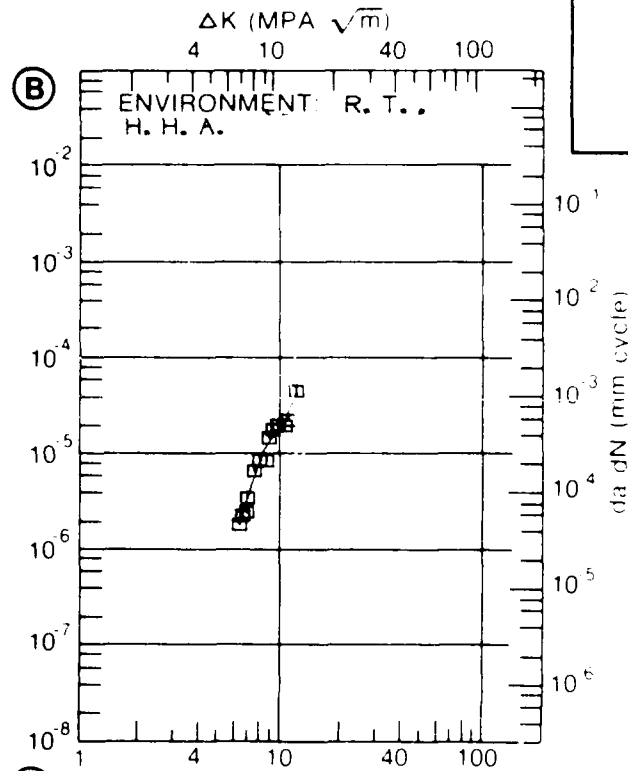
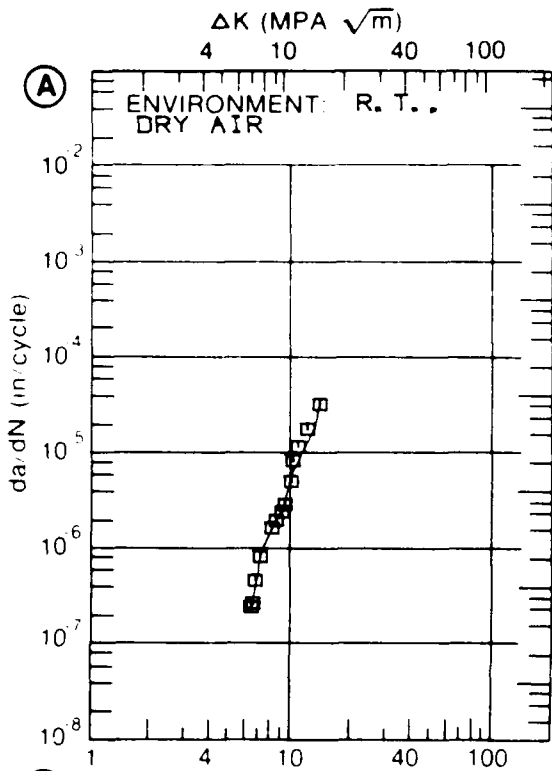


Figure 8.6.3.4

TABLE 8.6.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.5 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		7049			
CONDITION: T7351					
ENVIRONMENT: R T / L H A					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN /CYCLE)			
		A	B	C	D
		R=-1.00	R=+0.00	R=+0.50	
DELTA K	A: 5.51	584			
MIN	B: 5.71		454		
	C: 4.10			344	
	D:				
	5.00			765	
	6.00	635	515	171	
	7.00	894	795	343	
	8.00	1.40	1.21	6.13	
	9.00	2.26	1.79	9.87	
	10.00	3.59	2.58	14.6	
	13.00	11.5	6.57	30.7	
	16.00	24.2	13.6	49.2	
	20.00	43.9	28.3	108	
	25.00	85.6	56.9	336	
	30.00	179	101	827	
	35.00	330	171		
	40.00	507	289		
DELTA K	A: 47.38	1288			
MAX	B: 49.15		587		
	C: 34.04			833	
	D:				
ROOT MEAN SQUARE		9.31	15.85	12.92	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	02/0				

CONDITION/HT: T7351
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 10.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 72.0 KSI
 ULT. STRENGTH: 80.5 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: MA007

ALUM. ALLOY
7049

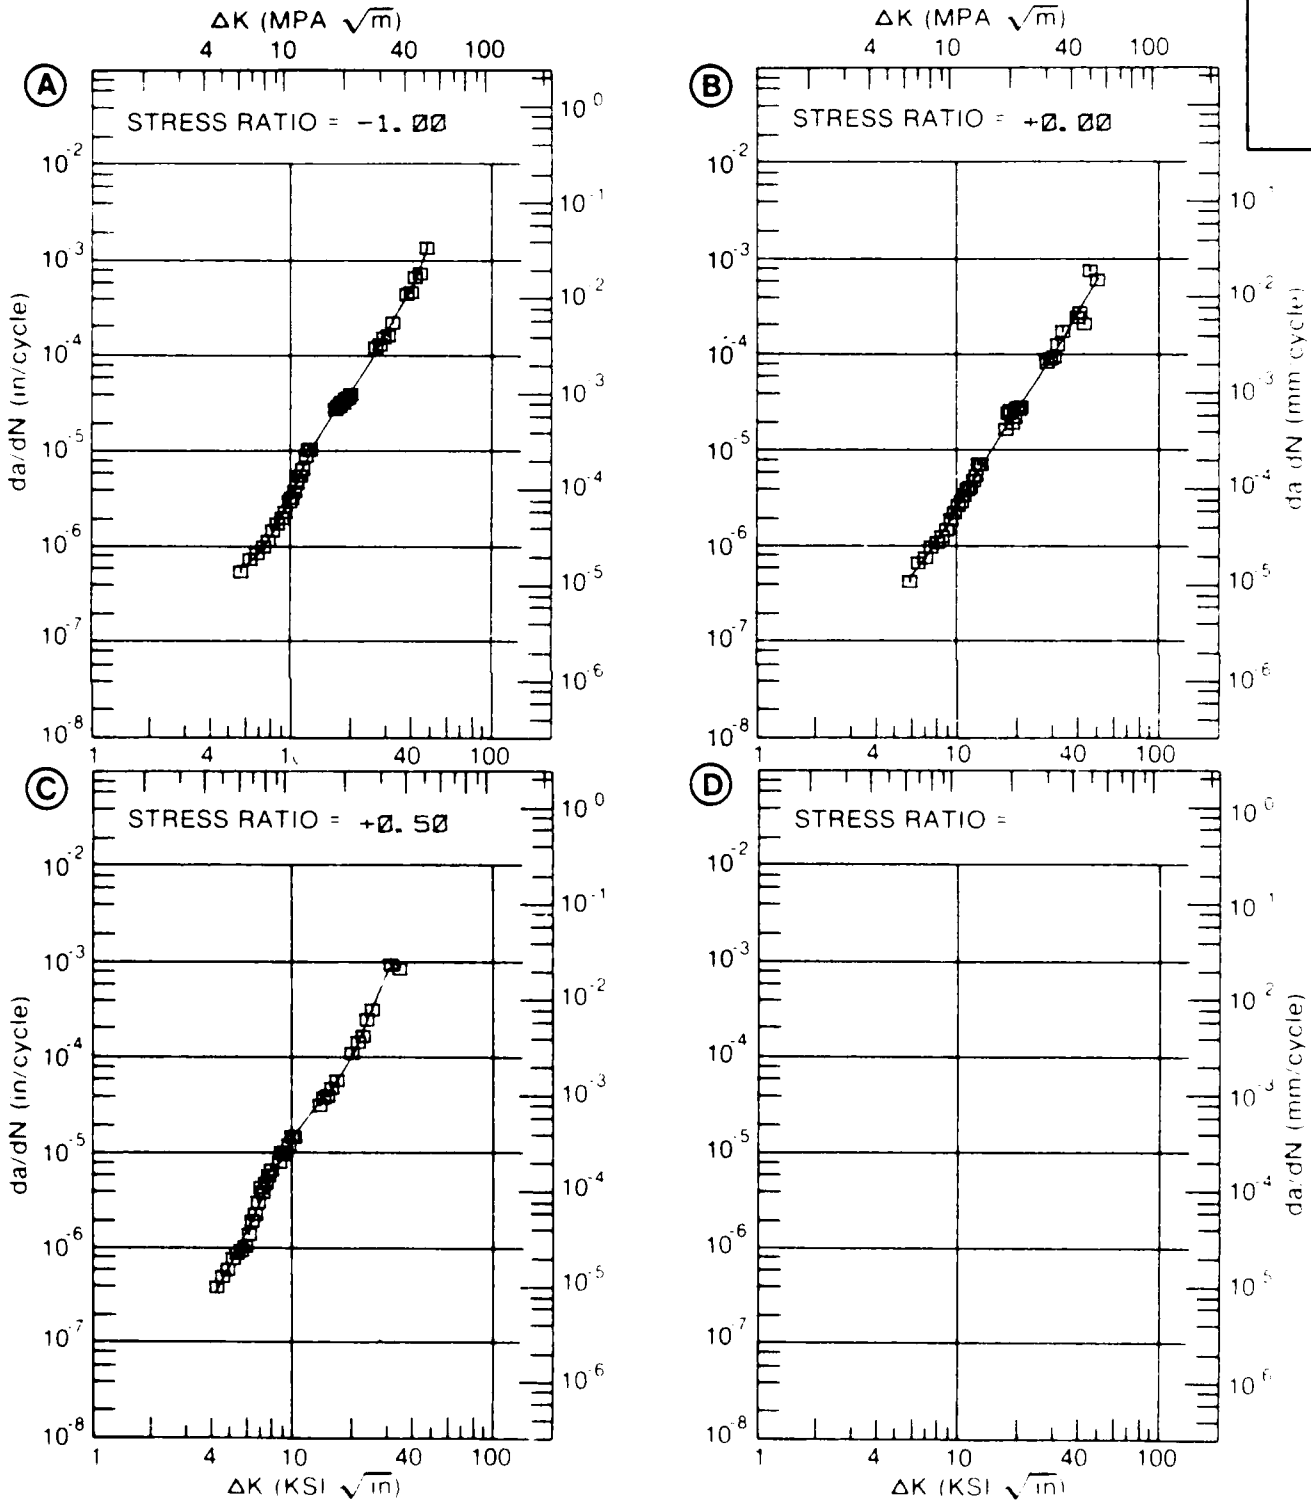


Figure 8.G.3.5

TABLE 8.6.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.6 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7049
CONDITION T7351
ENVIRONMENT R T 3 5% NaCl

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN /CYCLE)			
		A	B	C	D
		R=-1.00	R=+0.50		
DELTA K MIN	A: 5.59	2.34			
	B: 4.09		1.19		
	C:				
	D:				
	5.00		4.30		
	6.00	3.27	10.4		
	7.00	32	18.6		
	8.00	10.4	28.0		
	9.00	15.2	38.1		
	10.00	20.7	48.8		
	13.00	40.1	86.6		
	16.00	62.3	137		
	20.00	96.5	228		
	25.00	150	383		
	30.00	222	588		
	35.00	322	705		
	40.00	462			
DELTA K MAX	A: 48.22	833			
	B: 36.70		659		
	C:				
	D:				

ROOT MEAN SQUARE 18.32 14.87
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) 2.0

CONDITION/HT: T7351
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 0.10 HZ
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 72.0 KSI
 ULT. STRENGTH: 80.5 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: MA007

ALUM.
 ALLOY
 7049

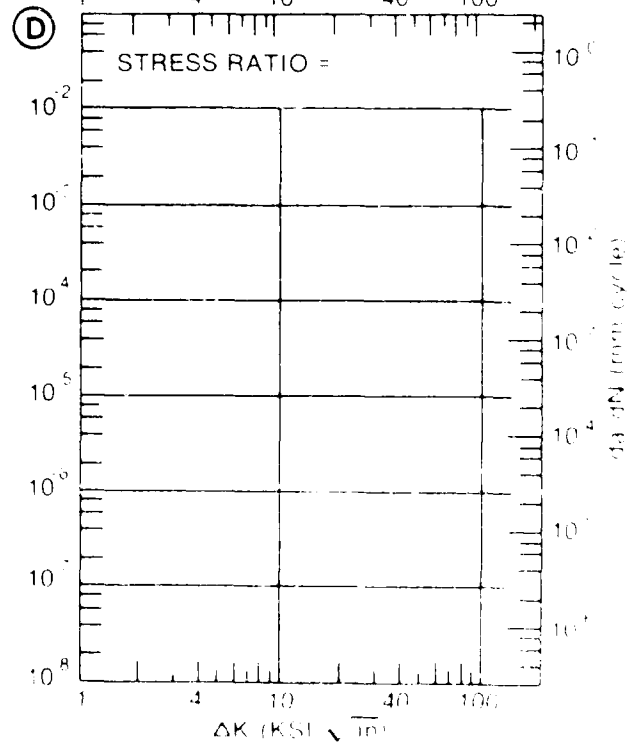
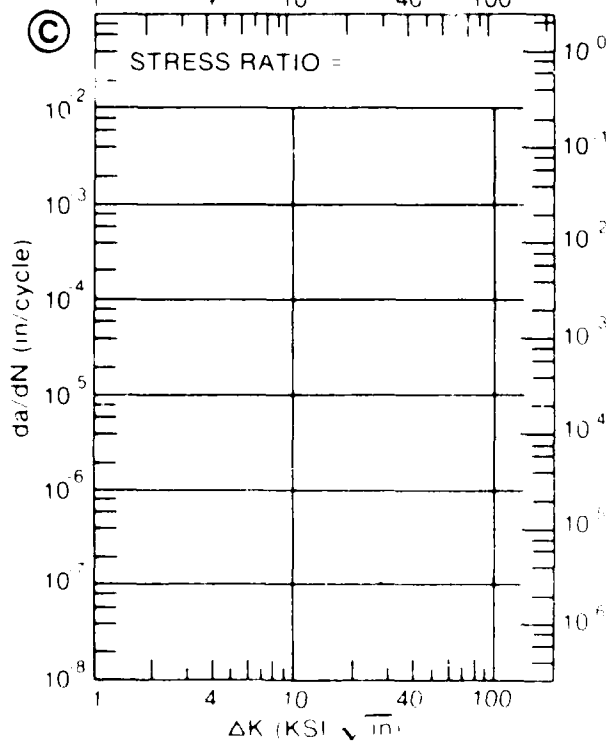
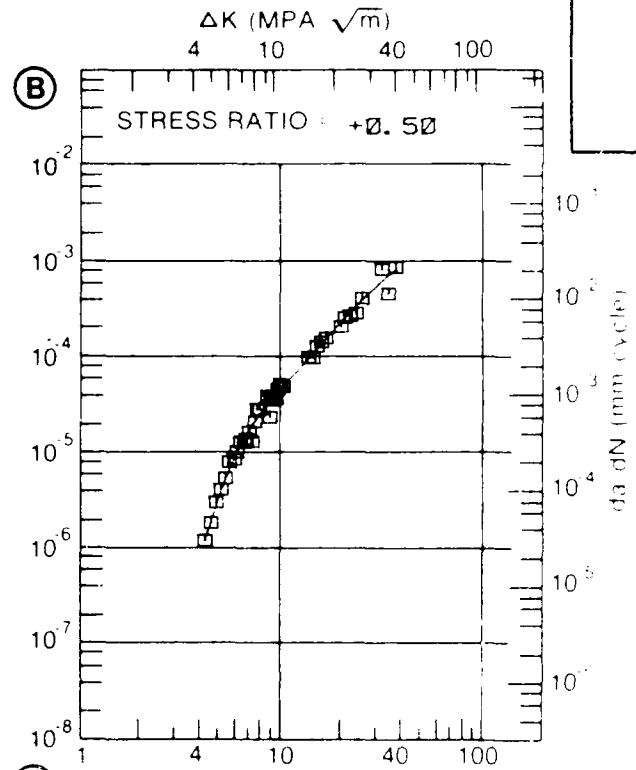
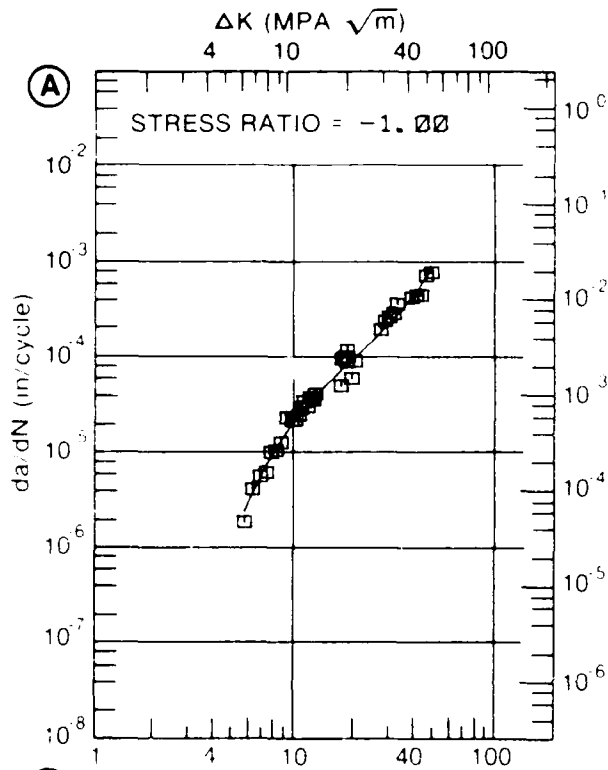


Figure 3.3.6

TABLE 8.6.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.7 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM 7047
CONDITION T7351
ENVIRONMENT: R T , 3 5% NaCl.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		(HZ)= 1.00		F(HZ)= 10.00	
DELTA K	A: 5.54	2.42			
MIN	B: 5.44		1.54		
	C:				
	D:				
	6.00	4.64	3.08		
	7.00	13.0	7.31		
	8.00	25.5	12.8		
	9.00	40.5	18.9		
	10.00	56.1	25.1		
	13.00	100.	44.3		
	16.00	145.	70.5		
	20.00	224.	125.		
	25.00	381.	212.		
	30.00	631.	295.		
	35.00	946.	384.		
	40.00	1268.	498.		
	50.00	2158.	928.		
	60.00	4564.	2129.		
DELTA K	A: 61.17	5082.			
MAX	B: 67.01		4311.		
	C:				
	D:				

ROOT MEAN SQUARE 18.36 14.62
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T7351
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.00
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 72.0 KSI
 ULT. STRENGTH: 80.5 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: MA007

ALUM.
ALLOY

7049

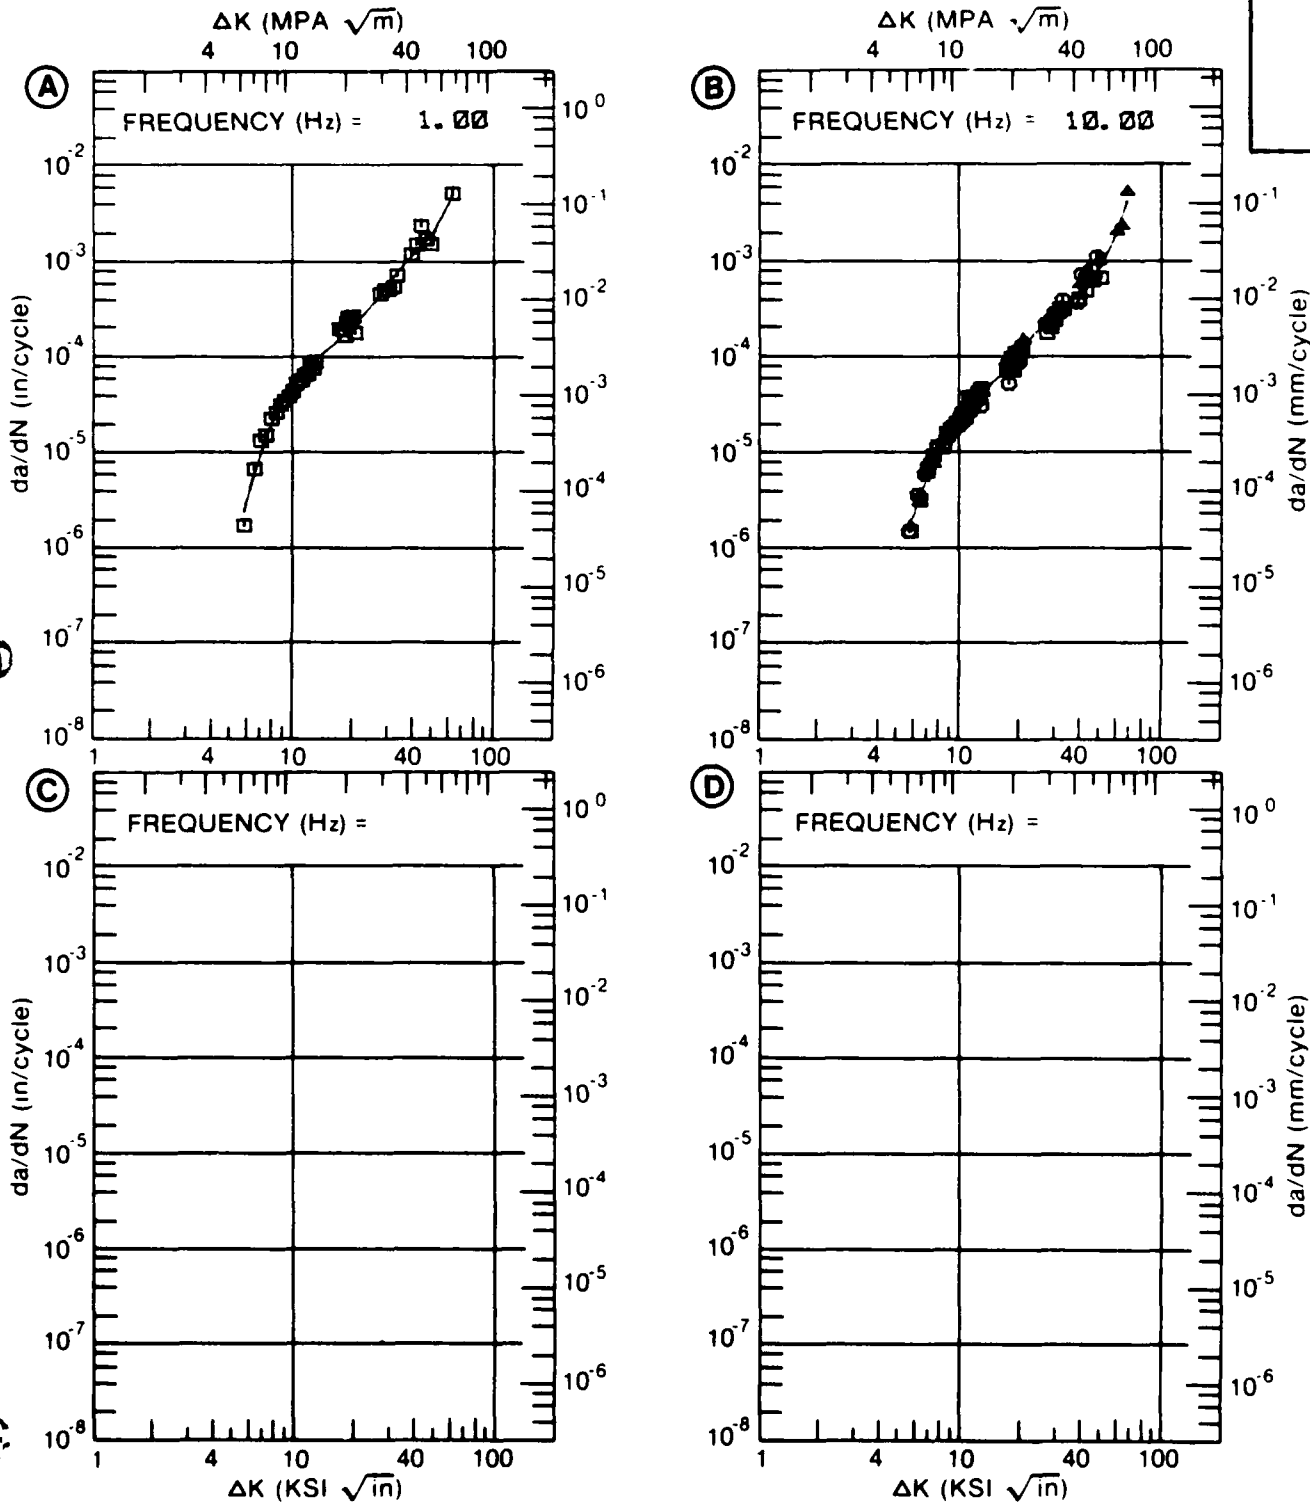


Figure 8.6.3.7

TABLE 8.6.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049					
CONDITION: T73511-HIGH PURITY					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. H. H. A.		
DELTA K	A: 5.95	.726			
MIN	B: 6.21		1.25		
	C:				
	D:				
	6.00	.792			
	7.00	2.72	3.06		
	8.00	5.00	6.55		
	9.00	6.72	10.8		
	10.00	7.84	15.4		
	13.00	11.5	29.0		
	16.00	19.0	46.3		
DELTA K	A: 18.73	28.2			
MAX	B: 18.07		65.8		
	C:				
	D:				
ROOT MEAN SQUARE		5.91	5.87		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T73511-HIGH PURITY
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 30.00

YIELD STRENGTH: 76.7 KSI
 ULT. STRENGTH: 83.9 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM.
ALLOY

7049




Figure 8.6.3.8

TABLE 8.6.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.9 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049
CONDITION: T73511-HIGH PURITY

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. ... LAB AIR			
DELTA K	A: 6.17	1.78			
MIN	B:				
	C:				
	D:				
	7.00	2.91			
	8.00	4.44			
	9.00	6.06			
	10.00	7.81			
	13.00	15.0			
	16.00	29.7			
DELTA K	A: 16.25	31.6			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 14.30
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73511-HIGH PURITY
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 30.00

YIELD STRENGTH: 70.3 KSI
 ULT. STRENGTH: 78.5 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM. ALLOY
7049

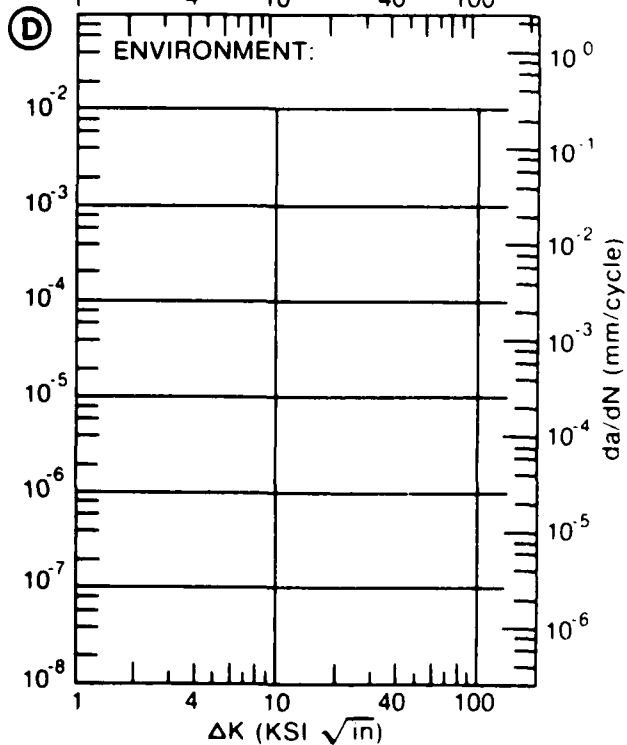
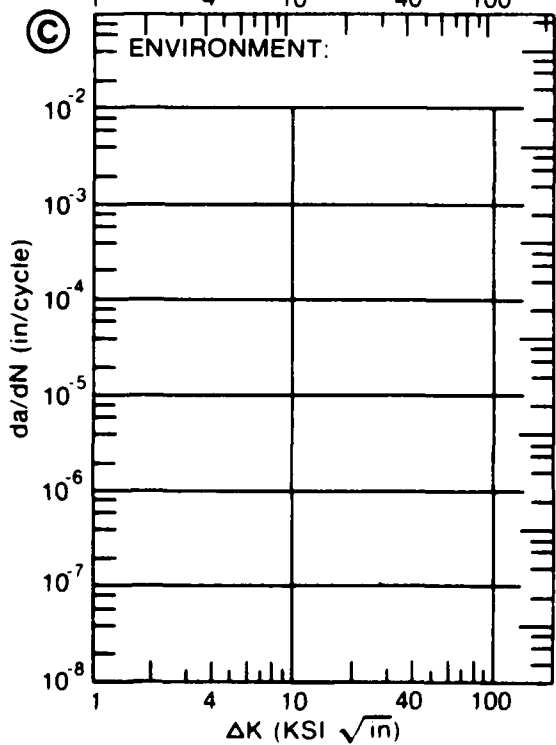
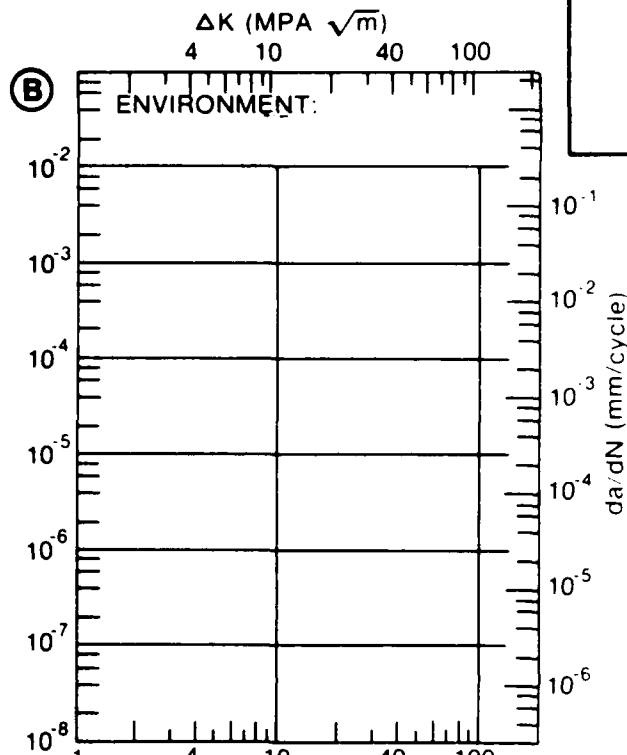
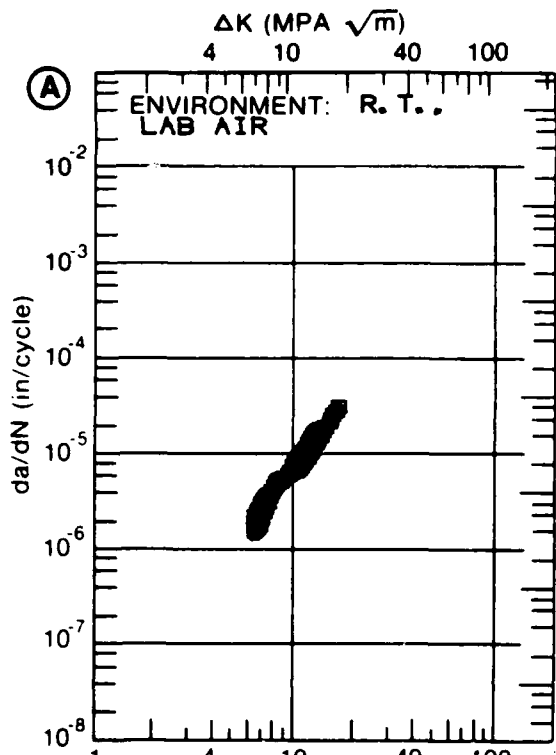


Figure 8.6.3.9

TABLE 8.6.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049
CONDITION: T73511-LOW PURITY

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR	E= R. T. H. H. A.		
DELTA K MIN	A: 6.10	.567		
	B: 5.94	.867		
	C:			
	D:			
	6.00		.944	
	7.00	1.80	2.83	
	8.00	3.78	5.55	
	9.00	5.76	8.56	
	10.00	7.32	11.5	
	13.00	10.2	19.9	
	16.00		32.3	
DELTA K MAX	A: 14.37	11.6		
	B: 16.99	38.8		
	C:			
	D:			
ROOT MEAN SQUARE PERCENT ERROR	11.79	8.70		

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73511-LDW
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 30.00

PURITY

YIELD STRENGTH: 73.1 KSI
 ULT. STRENGTH: 80.0 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM.
ALLOY

7049

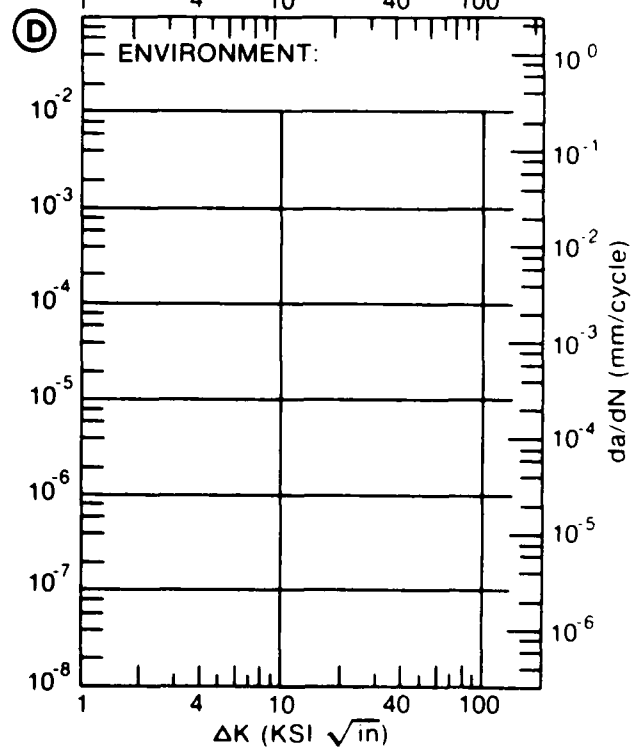
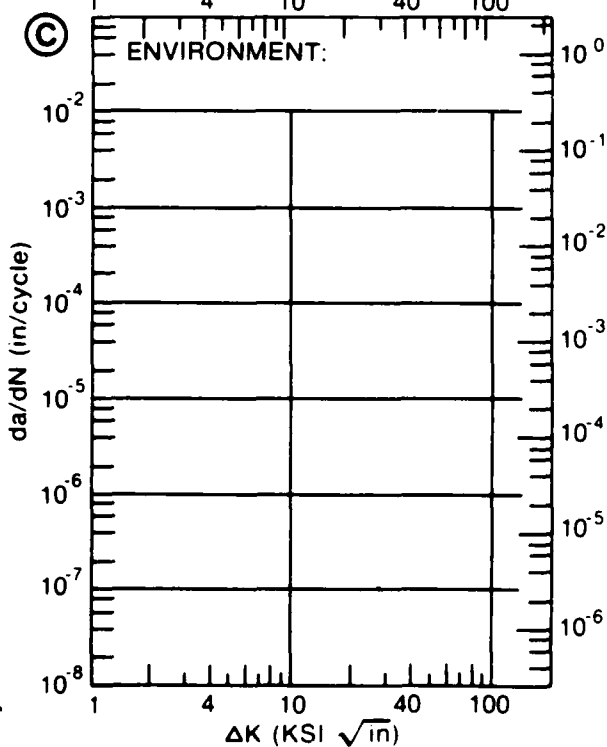
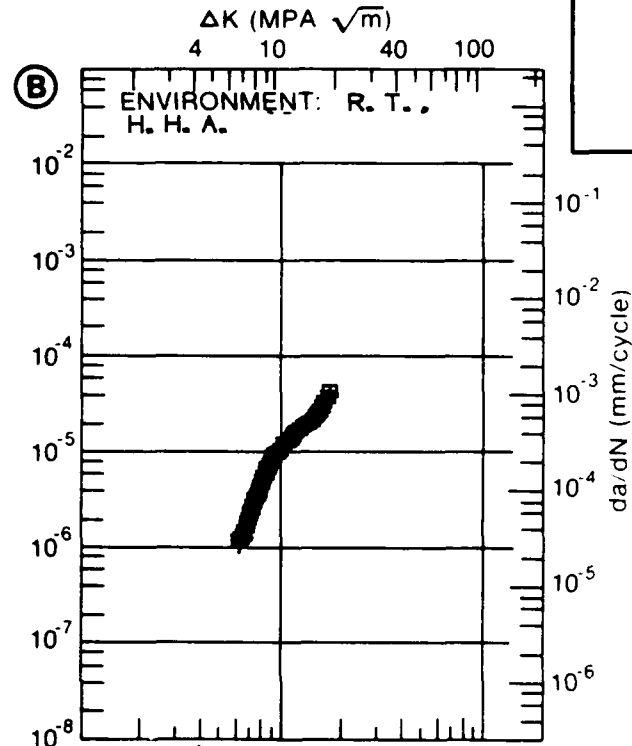
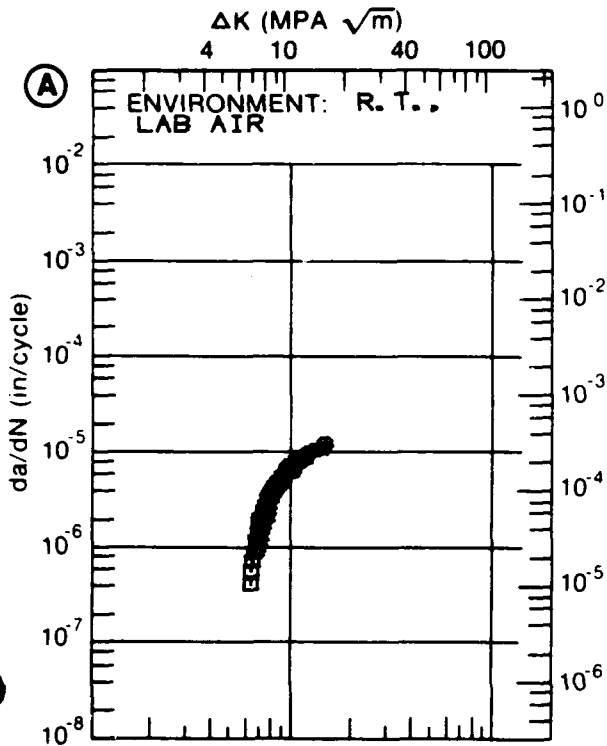


Figure 8.6.3.10

TABLE 8.6.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.11 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7049
CONDITION: T73511-LOW PURITY
ENVIRONMENT: R T, LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 6.07	1.39			
	B:				
	C:				
	D:				
	7.00	2.98			
	8.00	4.99			
	9.00	7.08			
	10.00	9.33			
	13.00	20.0			
DELTA K MAX	A: 14.70	33.5			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 7.33
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73511-LOW PURITY
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 30.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 68.6 KSI
 ULT. STRENGTH: 75.7 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM. ALLOY
7049

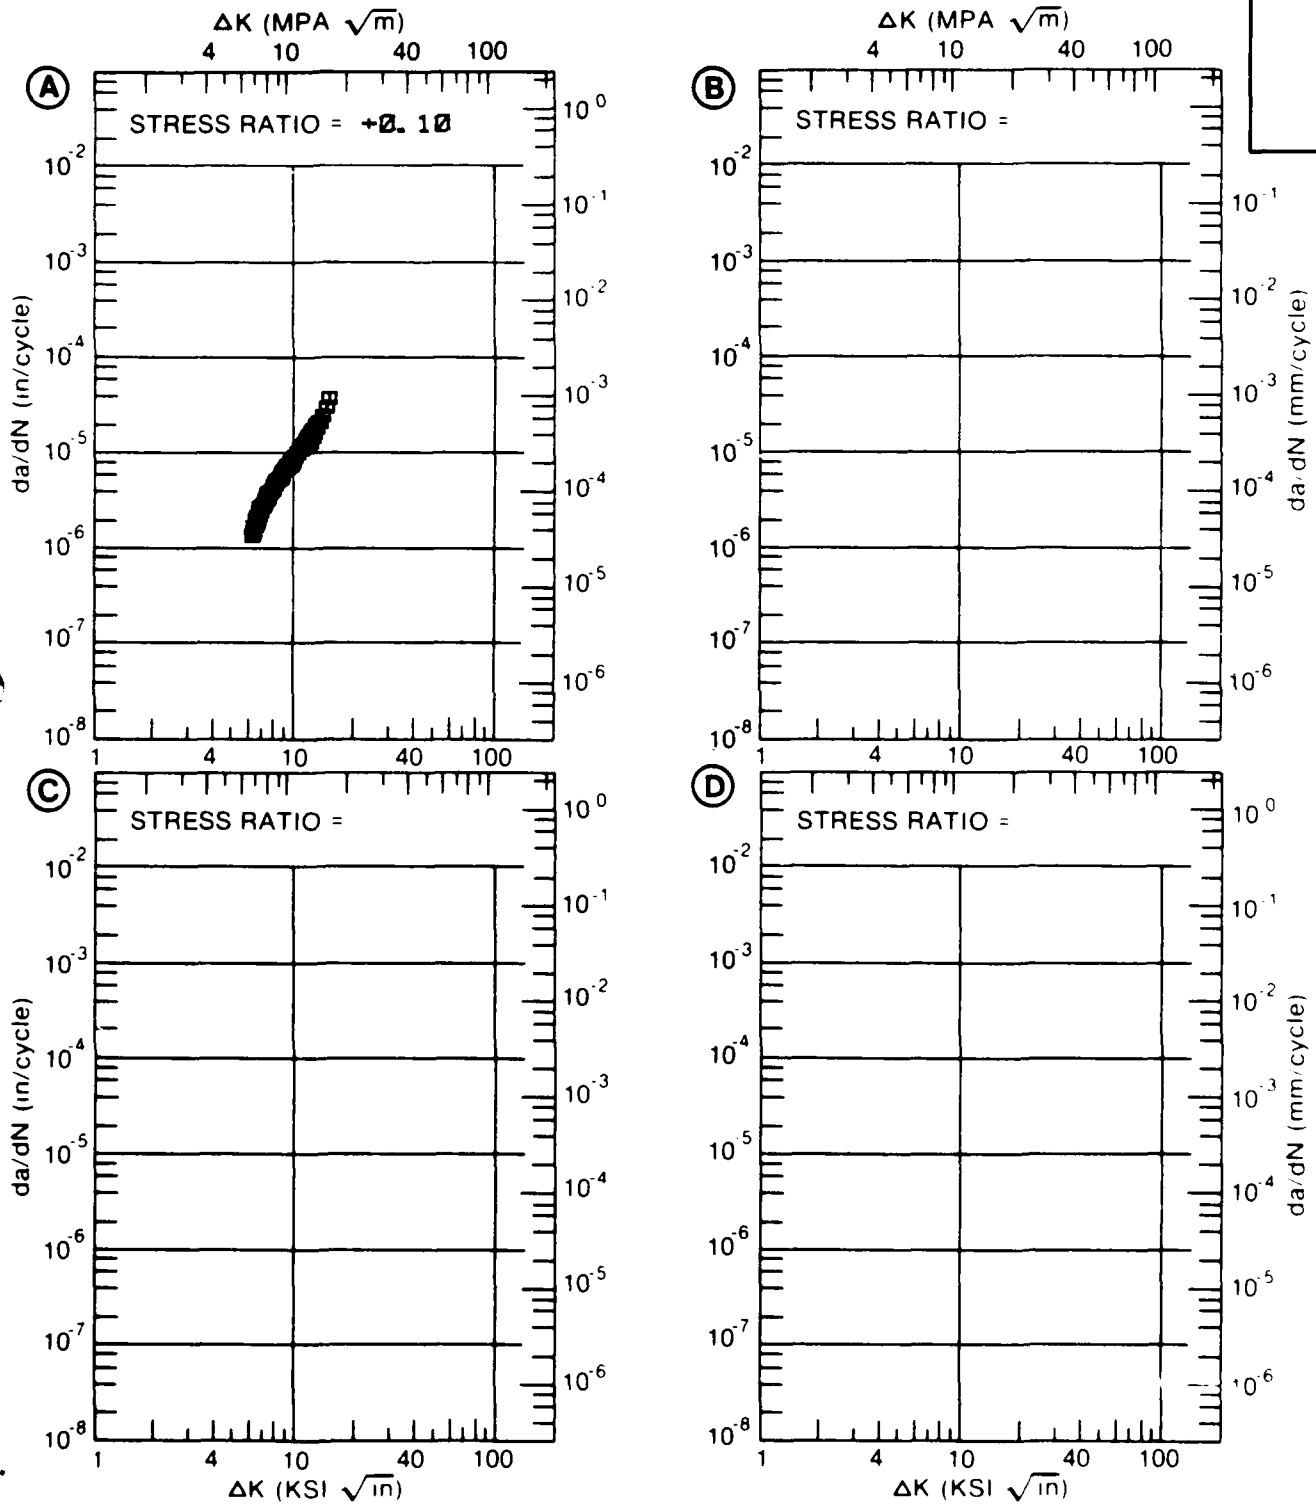


Figure 8.6.3.11

TABLE 8.6.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.12 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049
CONDITION: T73511-MEDIUM PURITY

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR	E= R. T. H. H. A.		
DELTA K MIN	A: 5.97 : .423	B: 1.41		
	6.00 : .435	1.44		
	7.00 : .969	3.55		
	8.00 : 1.68	6.61		
	9.00 : 2.52	10.3		
	10.00 : 3.44	14.2		
	13.00 : 6.65	25.3		
	16.00 : 11.2	34.3		
DELTA K MAX	A: 18.90 : 18.2	B: 38.5		
ROOT MEAN SQUARE PERCENT ERROR	22.36	9.47		

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73511-MEDIUM PURITY
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 30.00

YIELD STRENGTH: 75.4 KSI
 ULT. STRENGTH: 82.5 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM. ALLOY
7049

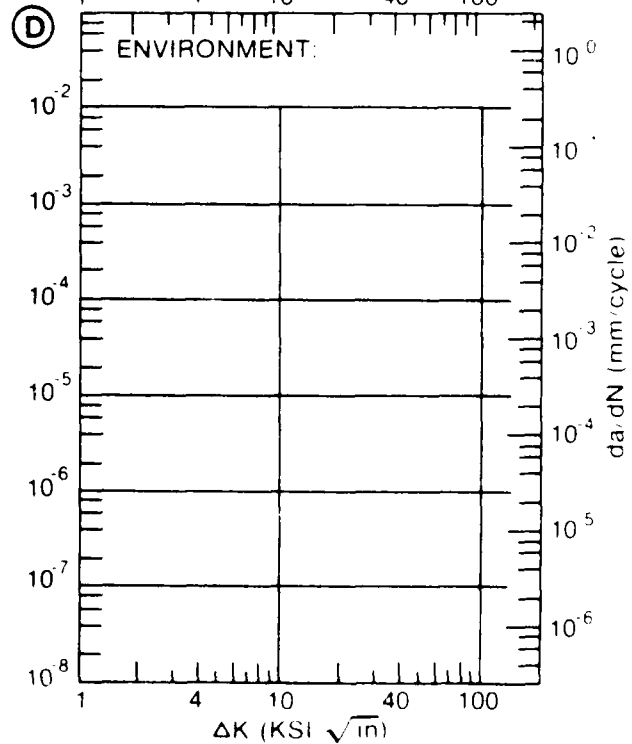
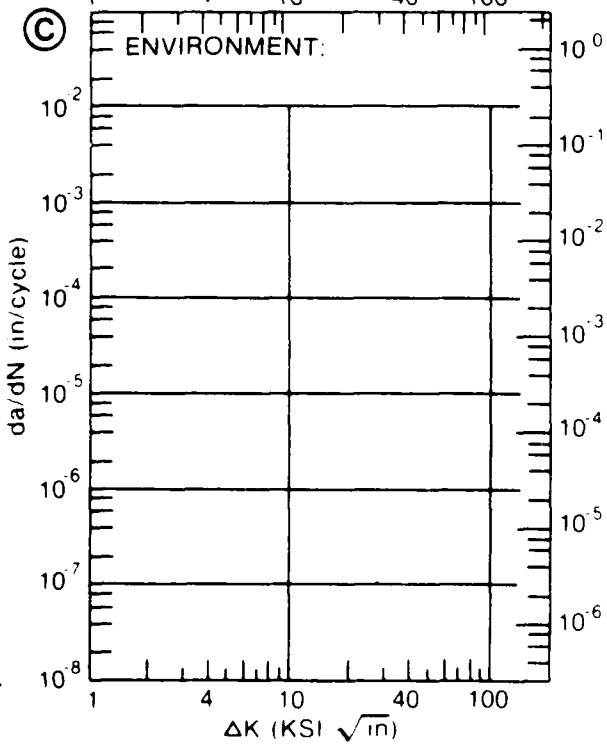
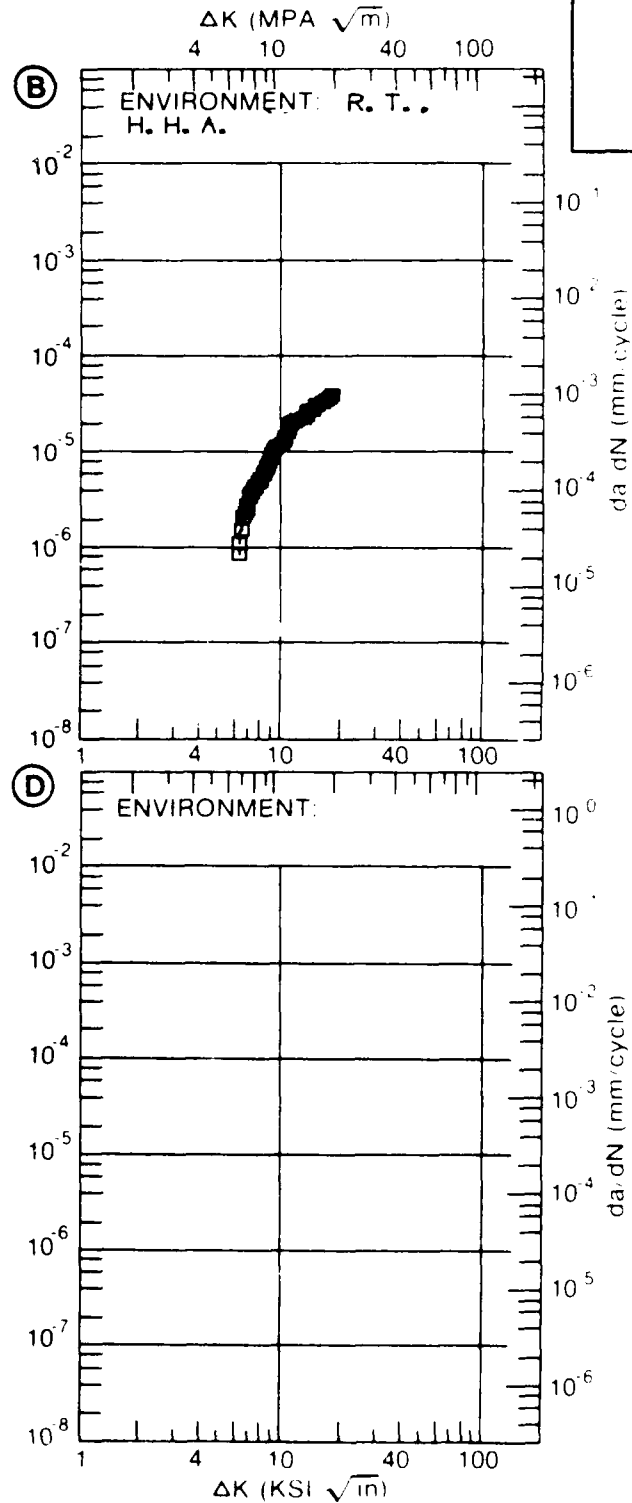
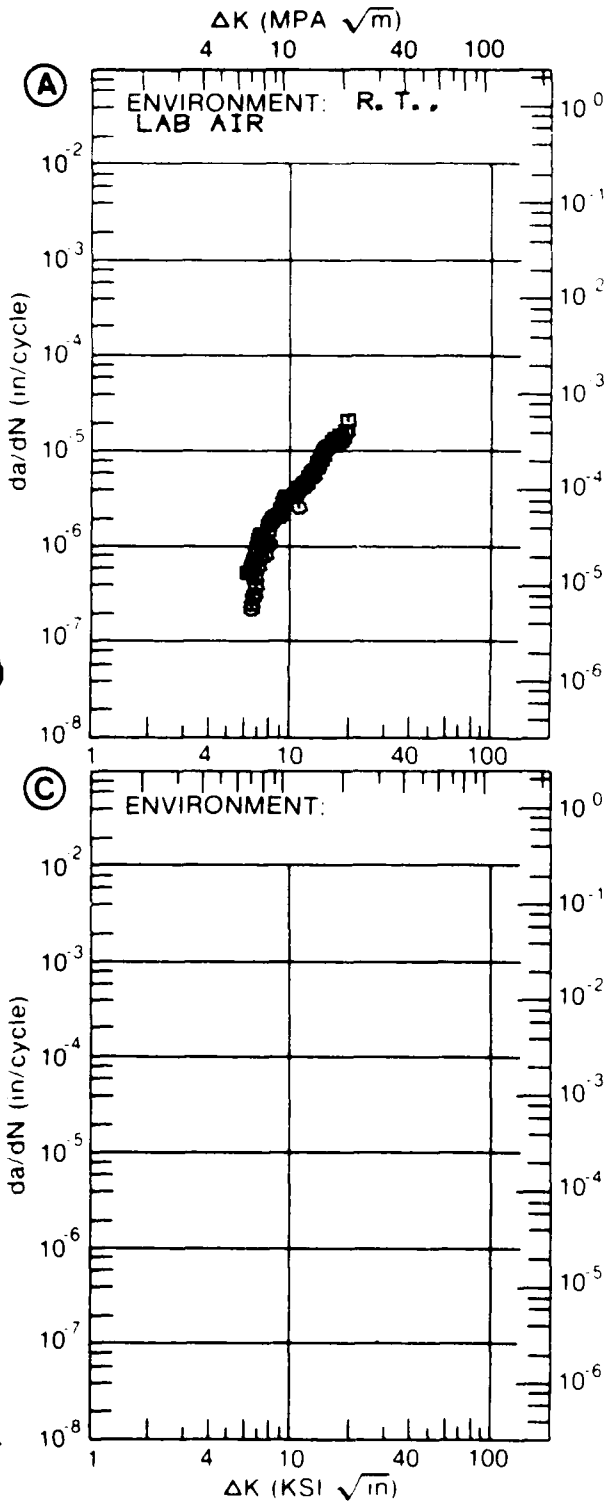


Figure 8.6.3.12

TABLE 8.6.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.13 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7049
CONDITION: T73511-MEDIUM PURITY
ENVIRONMENT: R T , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 6.21	1.59			
	B:				
	C:				
	D:				
	7.00	2.94			
	8.00	4.80			
	9.00	6.59			
	10.00	8.36			
	13.00	15.9			
	16.00	37.8			
DELTA K MAX	A: 16.60	46.6			
	B:				
	C:				
	D:				
ROOT MEAN SQUARE		11.31			
PERCENT ERROR					

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73511-MEDIUM PURITY
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 30.00
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 69.2 KSI
 ULT. STRENGTH: 76.5 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM.
ALLOY

7049

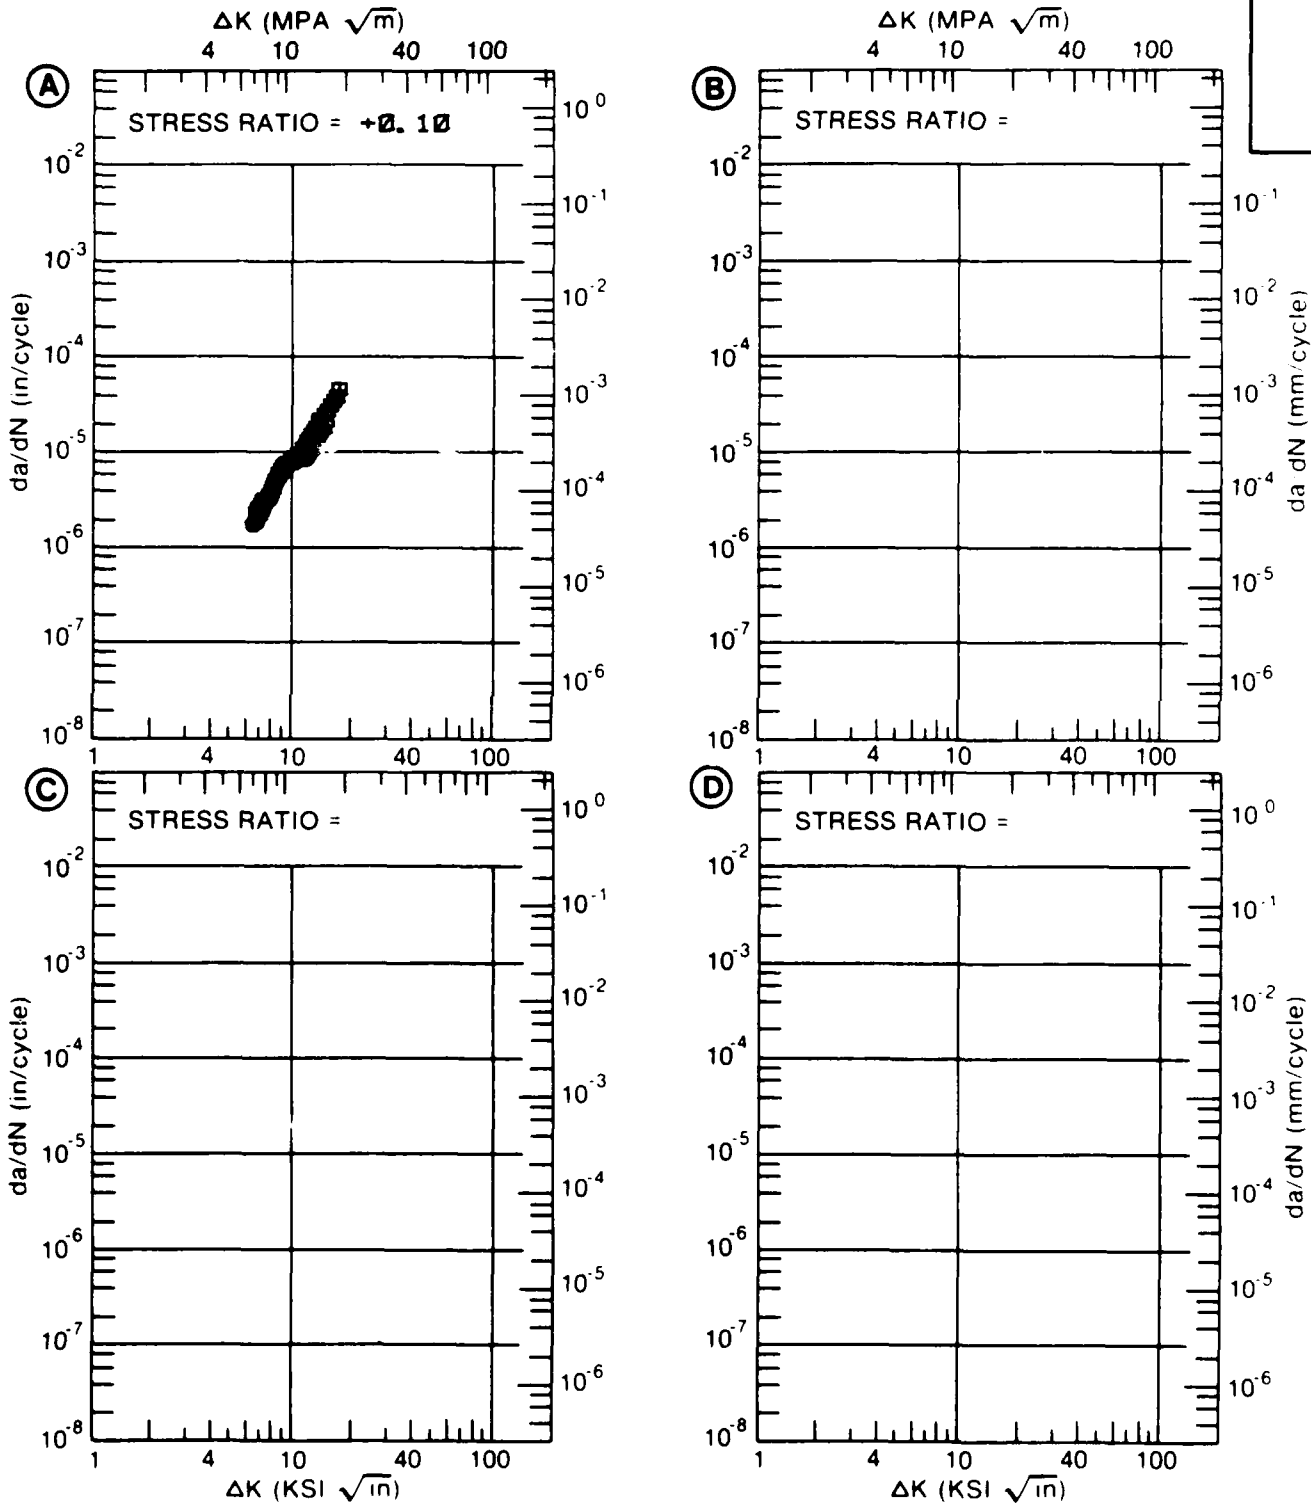


Figure 8.6.3.13

TABLE 8.6.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.14 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		7049			
CONDITION: T7352					
ENVIRONMENT: R.T., L.H.A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	
DELTA K MIN	A: 3.03	.199			
	B: 2.27		.0632		
	C: 2.36			.131	
	D:				
	2.50		.0652	.117	
	3.00		.232	.200	
	3.50	.242	.331	.498	
	4.00	.333	.491	.912	
	5.00	.666	1.03	1.29	
	6.00	1.21	1.93	2.59	
	7.00	1.91	3.29	5.39	
	8.00	2.80	5.20	8.14	
	9.00	3.99	7.76	9.42	
	10.00	5.63	11.0		
	13.00	15.8	25.9		
	16.00	16.0			
DELTA K MAX	A: 16.00	16.0			
	B: 15.87		47.6		
	C: 9.67			9.24	
	D:				
ROOT MEAN SQUARE		14.91	17.33	24.51	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	1	1	1	
	1.25-2.0				
	>2.0				

CONDITION/HT: T7352
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 65.0 KSI
 ULT. STRENGTH: 74.0 KSI
 SPECIMEN THK: 0.998- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837

ALUM.
ALLOY

7049

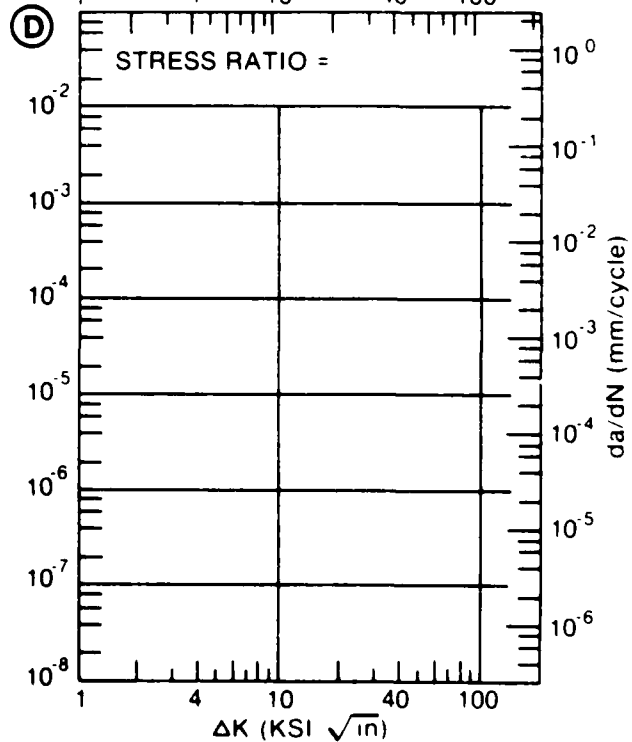
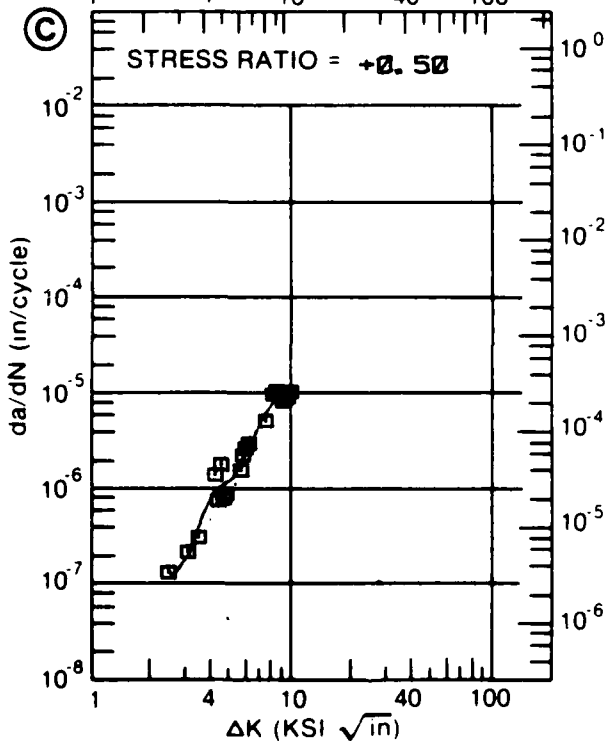
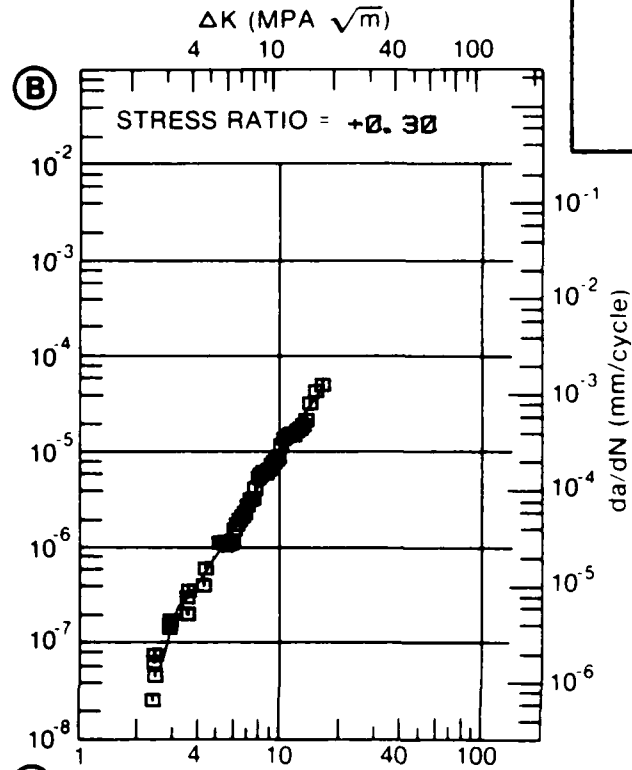
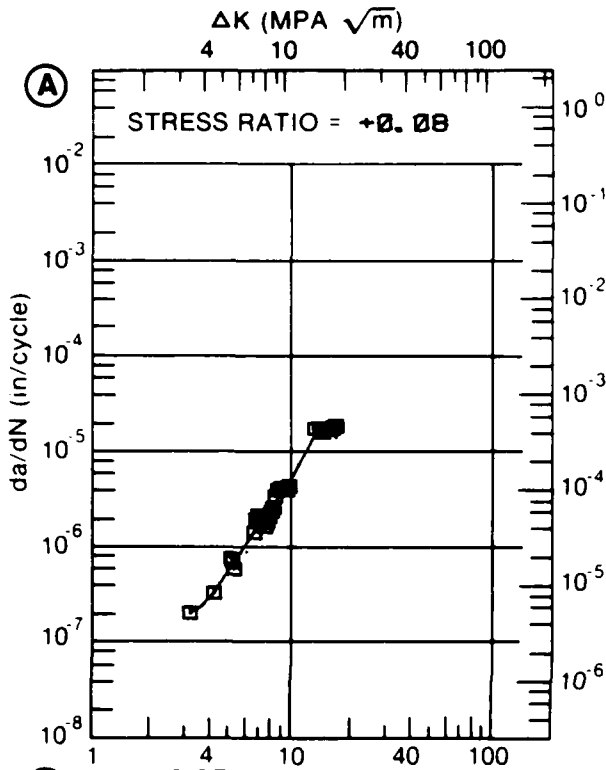


Figure 8.6.3.14

TABLE 8.6.3.15

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.15 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7049			
CONDITION: T7352					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. I. L. H. A. 6HZ	E= R. T. S. T. W. .1HZ		
DELTA K	A: 8.12	1.61			
MIN	B: 6.48		1.54		
	C:				
	D:				
	7.00		2.94		
	8.00		7.09		
	9.00	2.66	14.2		
	10.00	4.16	28.2		
	13.00	10.1			
	16.00	18.0			
	20.00	33.1			
DELTA K	A: 24.30	60.7			
MAX	B: 11.39		86.0		
	C:				
	D:				
ROOT MEAN SQUARE		6.86	15.34		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2			
SUMMARY	1.25-2.0		1		
(NP/NA)	>2.0				

CONDITION/HT: T7352
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 67.0 KSI
 ULT. STRENGTH: 76.0 KSI
 SPECIMEN THK: 0.250- 1.000"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 88579

ALUM.
ALLOY

7049

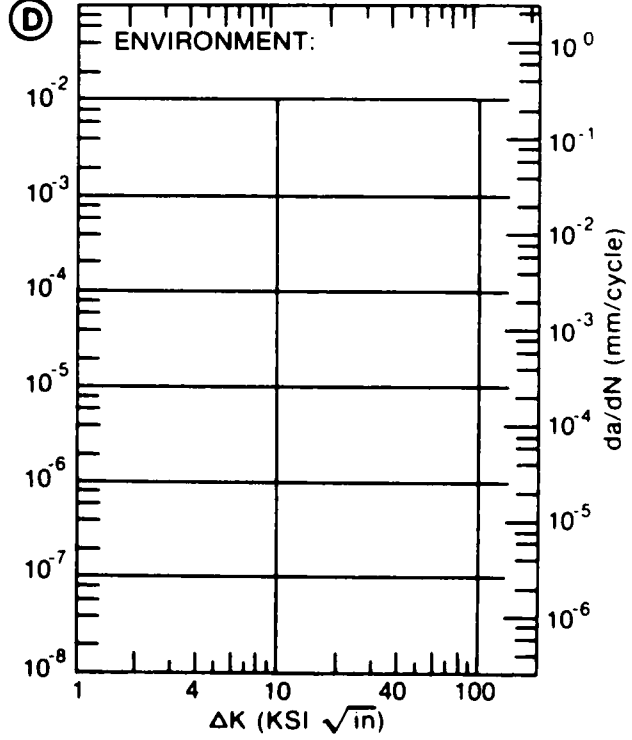
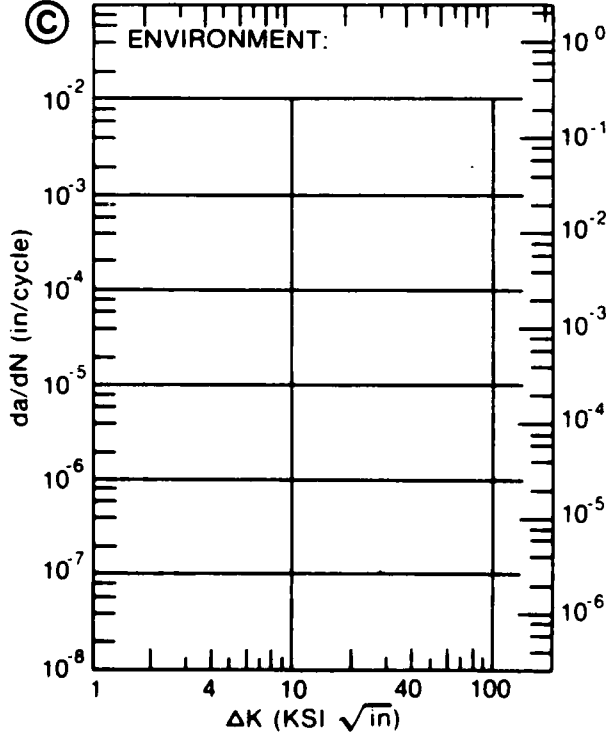
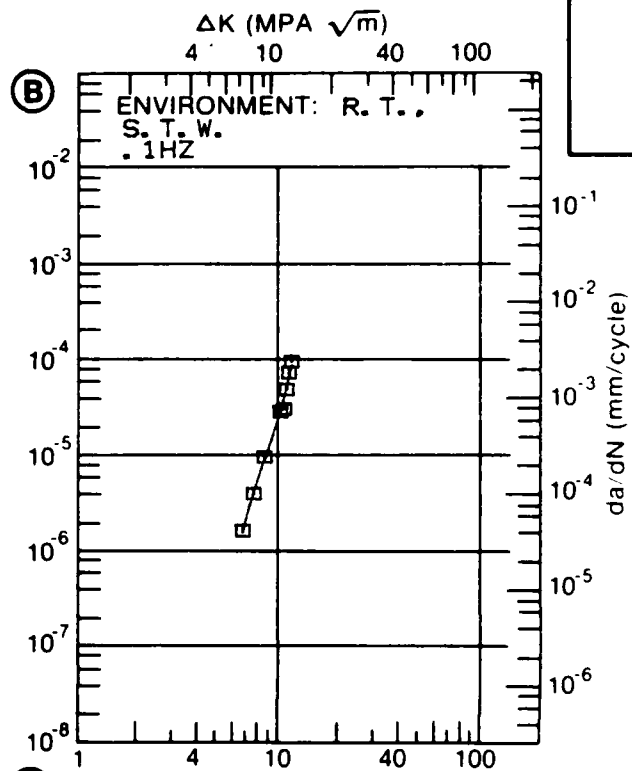
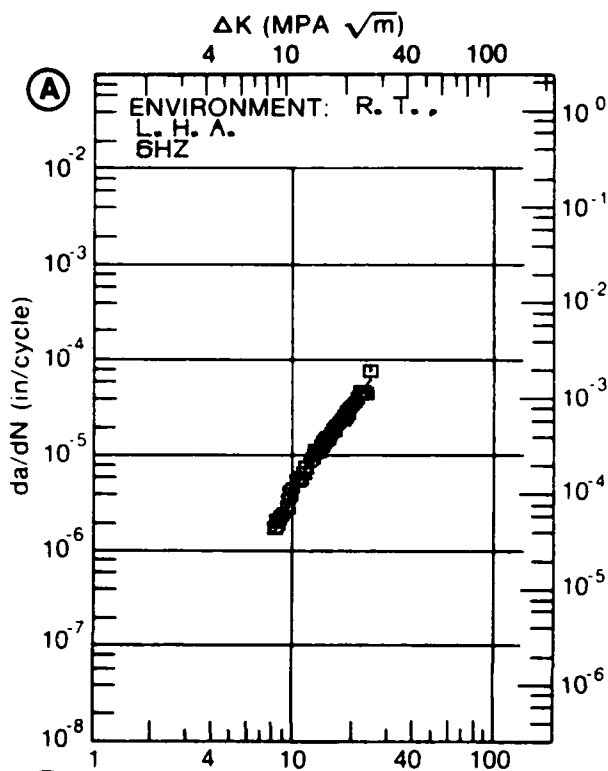


Figure 8.6.3.15

TABLE 8.6.3.16

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.16 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7049		
CONDITION: T7352				
DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.	E= R. T. S. T. W.		
DELTA K MIN	A: 6.47	B: 1.52	C:	D:
	7.00	2.66		
	8.00	5.52		
	9.00	9.01		
	10.00	13.0		
	13.00	32.9		
	16.00	100.		
DELTA K MAX	A: 17.21	B: 172.	C:	D:
ROOT MEAN SQUARE PERCENT ERROR		0.00	7.48	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1		

CONDITION/HT: T7352
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 64.0- 65.0 KSI
 ULT. STRENGTH: 73.0- 74.0 KSI
 SPECIMEN THK: 0.500- 0.990"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 85837, 88579

ALUM. ALLOY
7049

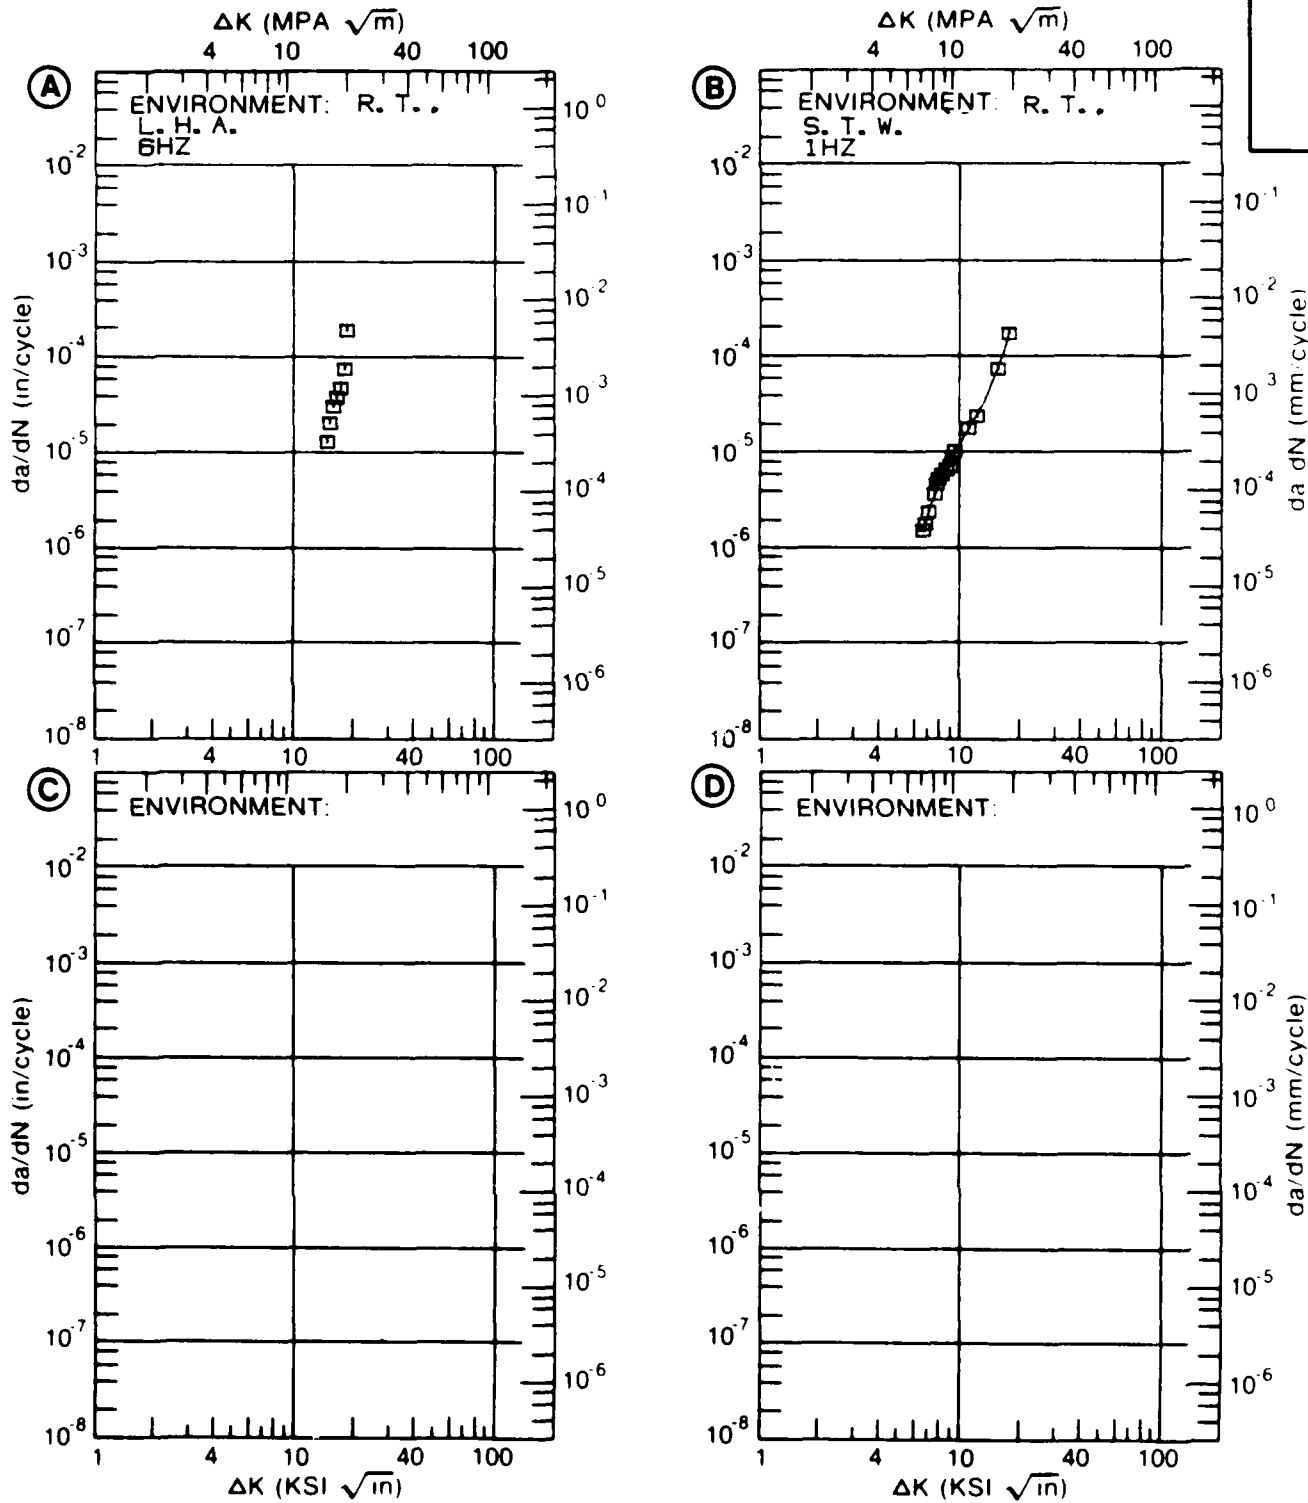


Figure 8.6.3.16

TABLE 8.6.3.17

SUSTAINED CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.6.3.17 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7049
CONDITION: T73

K MAX
(KSI*IN**1/2)

DA/DT (10**-6 IN/HOUR)

A

B

C

D

E=
WET 3X/DAY WITH
3.5% NaCl

K MAX A:
MIN B:
C:
D:

200.00

K MAX A:
MAX B:
C:
D:

ROOT MEAN SQUARE
PERCENT ERROR

0.00

CONDITION/HT: T73
 FORM: FORGING
 SPECIMEN TYPE: DCB
 ORIENTATION: S-L
 YIELD STRENGTH:
 ULT. STRENGTH:

SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 5.000"
 CRACK LENGTH (A₀):
 K_{ISCC}:
 REFERENCES: 84284

ALUM.
ALLOY

7049

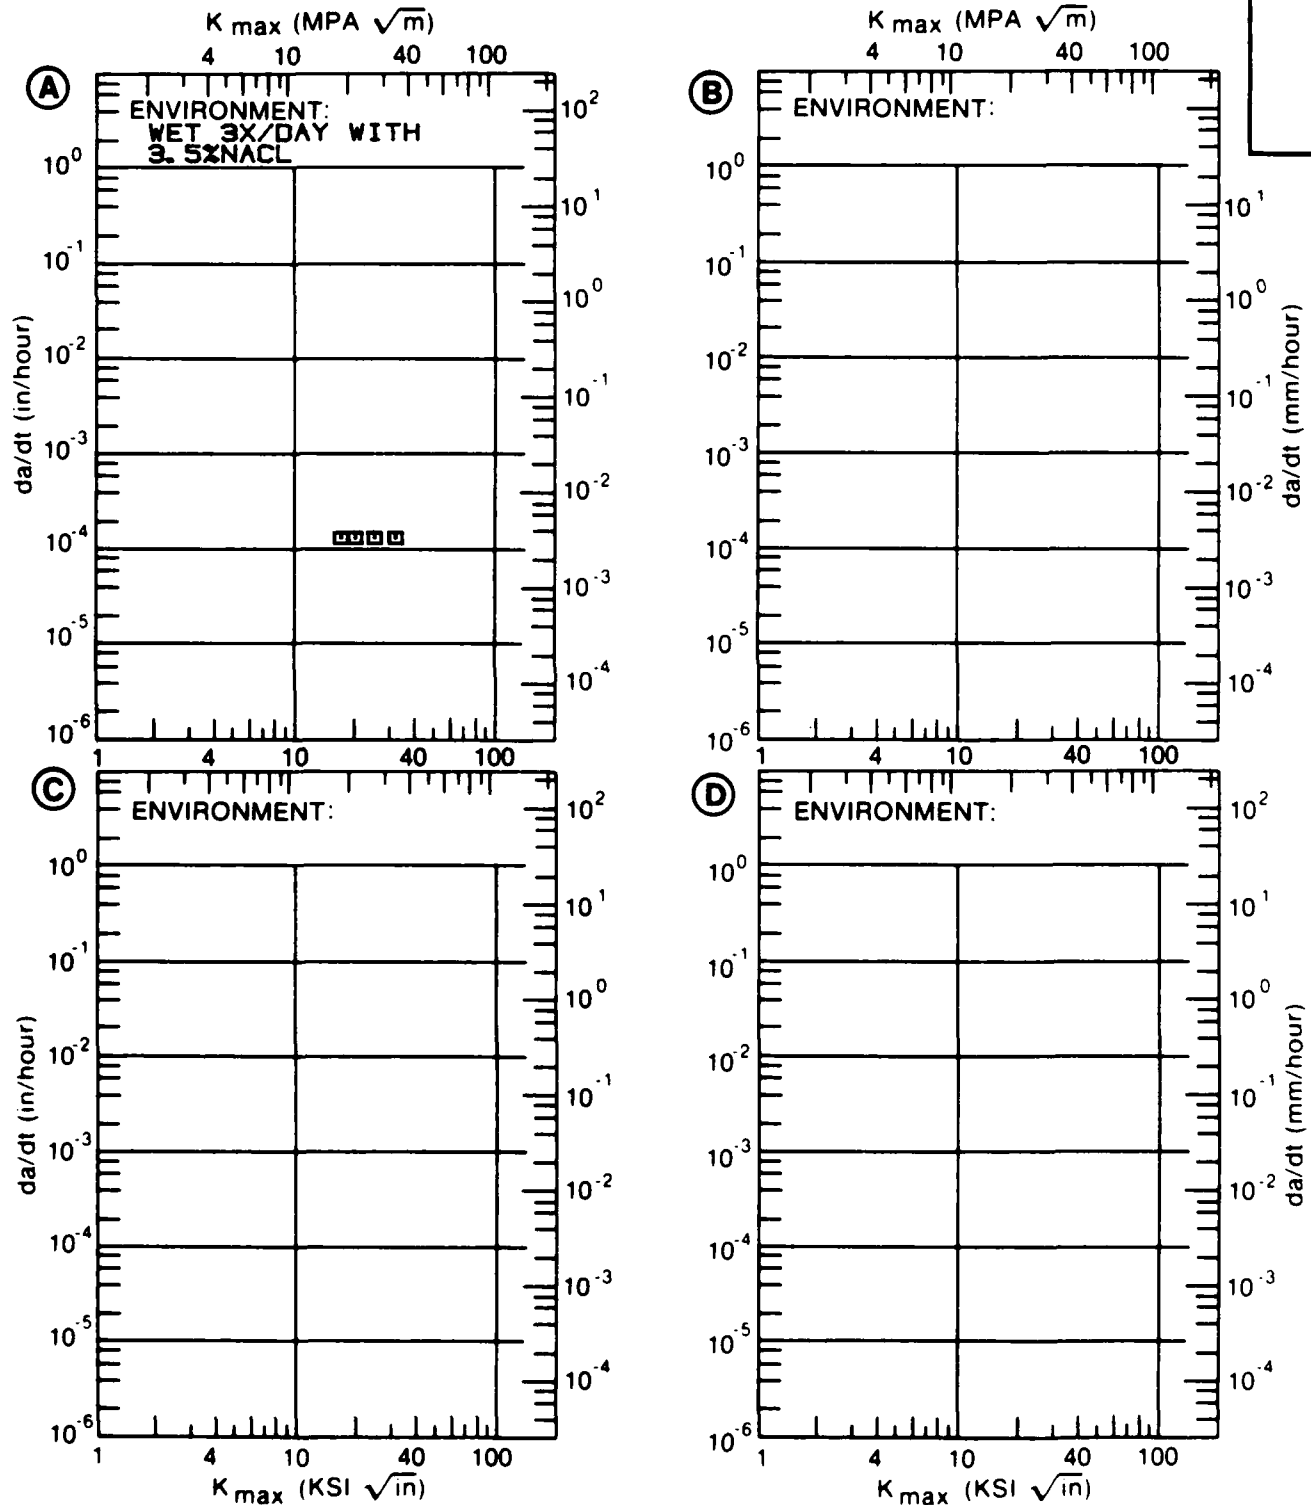


Figure 8.6.3.17

TABLE 8.6.3.18

CONDITION	--PRODUCT--		TEST SPEC OR STR (KSI)	YIELD	ENVIRONMENT	SPECIMEN		W	M	THICK (IN)	DESIGN LENGTH (IN) (**50)	CRACK LENGTH (IN) (K(SQRT IN))	K(I SCC)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	FORM	THICK (IN)				B	A										
T73	F	----	R. T.	S-L	68.9	3.5	PCT	NACL	1.000	0.500	CT	----	20.50	19.80		> 60660	1972 83242
T73	E	3.25	R. T.	L-B	73.4	3.5	PCT	NACL	2.000	1.000	CT	----	33.20	20.40		> 21280	1972 83061
T73	E	3.25	R. T.	S-L	65.4	3.5	PCT	NACL	2.000	1.000	CT	----	23.00	20.30		> 19800	1972 83061
T73 INTEGRALLY STIFFENED	E	3.00	R. T.	L-B	74.8	3.5	PCT	NACL	2.000	1.000	CT	----	28.10	26.70		> 17130	1972 83061
T73 INTEGRALLY STIFFENED	E	3.00	R. T.	S-L	68.6	3.5	PCT	NACL	2.000	1.000	CT	----	20.30	19.40		> 40230	1972 83061
T7352	F	3.00	R. T.	L-T	67.0	F. C. S.			5.500	1.000	DCB	----	41.00	> 27.50		76200	1976 R1006
T7352	F	3.00	R. T.	L-T	67.0	S. C. S.			5.500	1.000	DCB	----	41.00	> 28.50		76140	1976 R1006
T7352	F	3.00	R. T.	L-T	67.0	S. T. W.			5.500	1.000	DCB	----	41.00	> 25.50		76200	1976 R1006
T7352	F	3.00	R. T.	T-L	64.0	S. T. W.			5.500	1.000	DCB	----	41.00	> 27.60		76200	1976 R1006
T7352	F	3.00	R. T.	L-T	67.0	S. T. W.			5.500	1.000	DCB	----	41.00	21.00		133680	1976 R1006
T7352	F	3.00	R. T.	T-L	64.0	S. T. W.			5.500	1.000	DCB	----	41.00	19.50		133680	1976 R1006
T7352	F	3.00	R. T.	L-T	64.0	S. T. W.			5.500	1.000	DCB	----	41.00	> 21.50		133680	1976 R1006
T7352	F	3.00	R. T.	L-T	64.0	S. T. W.			5.500	1.000	DCB	----	41.00	> 20.00		133680	1976 R1006
T7352	F	3.00	R. T.	S-L	62.0	S. T. W.			5.500	1.000	DCB	----	41.00	19.00	19.3/ 0.4	133680	1976 R1006
T7352	F	3.00	R. T.	S-L	62.0	S. T. W.			5.500	1.000	DCB	----	39.00	17.50		133680	1976 R1006
T7352	F	3.00	R. T.	S-L	62.0	S. T. W.			5.500	1.000	DCB	----	39.00	> 17.50		133680	1976 R1006
T7352	F	3.00	R. T.	S-L	62.0	S. T. W.			5.500	1.000	DCB	----	39.00	> 22.50		61680	1976 R1006
T7352	F	3.00	R. T.	S-L	62.0	S. T. W.			5.500	1.000	DCB	----	39.00	17.00	17.3/ 0.4	133680	1976 R1006

TABLE 8.7.1.1.1

MEAN PLANE STRAIN FRACTURE TOUGHNESS DATA OF ALUMINUM ALLOY 7050 AT ROOM TEMPERATURE

CONDITION/HT	MEAN K _{IC} ± STANDARD (KSI SQRT(IN)) DEVIATION	(NUMBER OF SPECIMENS)		
		I-I	I-L	S-L
PLATE				
T7351	34.8 ± 3.9 (31)	30.0 ± 2.6 (29)	28.0 ± 1.3 (30)	
T73651	31.9 ± 3.9 (86)	28.7 ± 4.7 (83)	23.5 ± 1.5 (35)	
T7451	30.8 ± 0.3 (3)	-----	-----	-----
FORGING				
CONDITION/HT	I-I	I-L	S-L	
T/156	-----	28.9 ± 3.9 (4)	-----	
T736	32.3 ± 2.3 (4)	23.4 ± 1.0 (4)	24.6 ± 0.6 (6)	
T/3452	31.1 ± 2.5 (11)	20.7 ± 1.4 (13)	19.2 ± 1.4 (17)	
EXTRUDED BAR				
CONDITION/HT	I-I	I-L	S-L	
T/3511 HIGH/ PURITY	35.2 ± 3.2 (2)	24.1 ± 0.2 (2)	-----	

TABLE 8.7.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION L T

ENVIRONMENT DRY AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
T7351	PLATE	0.33	2.00-20.00		6.92 62.1
T735	FORGING	0.10	20.00		29.1
T7351	PLATE	0.10	20.00		9.52
T76	SHEET	0.33	13.30		14.0
T7651	PLATE	0.10	20.00		9.43 41.0

TABLE 8.7.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECTRUM
ORIENTATION L T

ENVIRONMENT L H A
A T R T

CONDITION/PI	PRODUCT FORM	STRESS RATIO	FREQ (Hz)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2	5	10	20	50	100
17301X	FORGING	0.08	6.00							12.6
17301X	EXTRUSION	0.33	20.00		0.49	3.48				
173511	EXTRUSION	0.10	8.00-50.00		0.22	2.71	32.0			
173511	EXTRUSION	0.33	7.50-15.00		0.33	2.08				
173511	EXTRUSION	0.59	8.00-50.00		0.08	0.77	9.86			
173651	PLATE	0.08	6.00				2.61	26.0		
173651	PLATE	0.30	6.00		0.37	4.62				
173651	PLATE	0.33	18.10			2.39				
173651	PLATE	0.50	6.00			1.35				
173651X	EXTRUSION	0.33	30.00		0.50	3.49				
173651	EXTRUSION	0.33	18.10			3.45				
173651	EXTRUSION	0.33	18.30		0.41	3.95				
173651	EXTRUSION	0.46	18.30			4.90				

TABLE 8.7.1.4

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION	L T	ENVIRONMENT	LAB AIR AT R T	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)						
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
T73511-HIGH PURITY	EXTRUSION	0.10	30.00							5.93
T736	FORGING	0.10	3.00-10.00					11.9		98.7
T73651	PLATE	0.10	3.00-25.00			0.82	4.09	48.7		
T73651	PLATE	0.10	5.00-10.00				7.68	47.3		
T76	SHEET	0.00	13.30					7.60	40.1	
T76	SHEET	0.33	13.30					10.4	70.3	
T7651	PLATE	0.02	1.00-20.00			0.58	8.04	22.9		

TABLE 8.7.1.5

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION L-T ENVIRONMENT H.H.A. AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2.5 5 10 20 50 100	
T7351	PLATE	0.10	2.00		6.79 42.1
T7351X	EXTRUSION	0.33	20.00		1.21 15.9
T73511	EXTRUSION	0.10	2.00		5.31 45.5 1663
T73511	EXTRUSION	0.10	15.00		0.45 5.85
T73511	EXTRUSION	0.10	10.00-20.00		5.16 45.5
T73511	EXTRUSION	0.10	50.00		0.29
T73511	EXTRUSION	0.33	15.00-20.00		0.63 8.94
T73511	EXTRUSION	0.50	15.00-20.00		0.11 1.04 10.9
T73511-NIGH PURITY	EXTRUSION	0.10	30.00		12.2
T73651	PLATE	0.33	18.30		12.7
T73651	PLATE	0.33	25.00	0.06	1.55 15.7 82.9
T73651	PLATE	0.33	25.00		1.03 12.9 63.3
T73651	EXTRUSION	0.10	2.00		0.33 5.81 49.0

TABLE 8.7.1.5 (Con't)

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT H.H.A
A.T.R.T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100
T76	SHEET	0.33	13.30							26.7
T7651	PLATE	0.10	2.00				7.27	70.8		
T7651	PLATE	0.10	20.00		0.33	9.75	52.1			
T7651X	EXTRUSION	0.33	20.00		1.68	16.6				
T76511	EXTRUSION	0.10	2.00			4.71	46.3	1946		
T76511	EXTRUSION	0.10	20.00		0.15	4.47	46.8			
T76511	EXTRUSION	0.33	18.30			16.8				
T76511	EXTRUSION	0.33	18.30		0.79	15.4				

TABLE 8.7.1.6

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT S.T.W. AT R.T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2	5	10	20	50	100	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
T7351	PLATE	0.33	2.00-20.00								20.4
T73651	PLATE	0.10	1.00-10.00								1.12 17.5 79.3

TABLE 8.7.1.7

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION L T

ENVIRONMENT SIM SEA WATER AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
T73651	PLATE	0.10	1.00-10.00	2.5 5 10 20 50 100	1.49 18.2 164
T7651	PLATE	0.02	1.00-20.00		10.6 64.2

TABLE 8.7.1.8

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION L-T

ENVIRONMENT SALT FOG AT R. T.

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)					
					2.5	5	10	20	50	100
173651	PLATE	0.33	18.30							20.8
176	SHEET	0.33	13.30							33.3
176511	EXTRUSION	0.33	18.30							17.1
176511	EXTRUSION	0.33	18.30						2.56	23.5

TABLE 8.7.1.9

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION T I

ENVIRONMENT DRY AIR AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
T7351	PLATE	0.33	1 50-20 00		8.65
T73652	FORGING	0.33	18 30		8.91
T76	SHEET	0.33	13 30		0.99 7.26

TABLE 8.7.1.10

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION T L

ENVIRONMENT L H A
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2 5	5	10	20	50	100
--------------	--------------	--------------	-----------	-------------------------------	-----	---	----	----	----	-----

T6	SMFET	0.33	13.30				11.9	114		
----	-------	------	-------	--	--	--	------	-----	--	--

T7351X	EXTRUSION	0.33	20.00			1.06	7.69			
--------	-----------	------	-------	--	--	------	------	--	--	--

T7351X	EXTRUSION	0.33	20.00			0.86	9.90			
--------	-----------	------	-------	--	--	------	------	--	--	--

T73511	EXTRUSION	0.33	7.50-20.00			0.53	6.86			
--------	-----------	------	------------	--	--	------	------	--	--	--

T73511	EXTRUSION	0.50	10.00-40.00		0.06	0.32	6.54			
--------	-----------	------	-------------	--	------	------	------	--	--	--

T73651	PLATE	0.08	6.00			0.24	2.87			
--------	-------	------	------	--	--	------	------	--	--	--

T73651	PLATE	0.33	18.30			0.52	6.75			
--------	-------	------	-------	--	--	------	------	--	--	--

T73651	PLATE	0.33	18.30				12.0			
--------	-------	------	-------	--	--	--	------	--	--	--

T7651X	EXTRUSION	0.33	20.00			0.88	5.65			
--------	-----------	------	-------	--	--	------	------	--	--	--

T76511	EXTRUSION	0.33	18.30			0.81	6.38			
--------	-----------	------	-------	--	--	------	------	--	--	--

TABLE 8.7.1.11

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION T-L

ENVIRONMENT LAB AIR AT R T

CONDITION/H1	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
T73511-HIGH PURITY	EXTRUSION	0 10	30 00		3 97
T736	FORGING	0 10	10 00		6 75 101
T73651	PLATE	0 10	1.00-10.00		8 45 49 4

TABLE 8.7.1.12

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION T-L ENVIRONMENT H.H.A. AT R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	2.5	5	10	20	50	100
T6	SHEET	0.33	13.30				21.3	163		
T6	SHEET	0.33	13.30				20.8	220		
T7351	PLATE	0.33	1.50-20.00				11.2			
T7351X	EXTRUSION	0.33	20.00				2.25	18.4		
T7351X	EXTRUSION	0.33	20.00				1.41	16.6		
T73511	EXTRUSION	0.33	7.50-20.00				0.85	12.4		
T73511	EXTRUSION	0.50	10.00-40.00		0.06		0.76	17.9		
T73651	PLATE	0.33	18.30				0.94	15.5		
T73651	PLATE	0.33	18.30					15.3		
T73652	FORGING	0.33	18.30					16.3		

TABLE 8.7.1.12 (Con't)

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION T I

ENVIRONMENT H H A
A T R I

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (Hz)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICR) IN (CYCLE)
				5	1
				5	20
				5	50
				5	100
T76	SHEET	0.33	13.30		1.6
T76S1X	EXTRUSION	0.33	20.00		2.05
T76S11	PLATE	0.33	18.30		1.7
T76S11	EXTRUSION	0.33	18.30		2.5

TABLE 8.7.1.13

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION T L ENVIRONMENT S T W A T R F

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN./CYCLE)
T7351	PLATE	0.33	150-2000	2.5 5 10 20 50 100	1.72 21.0
T73651	PLATE	0.08	100		13.3
T73651	PLATE	0.10	100-1000		1.16 15.9 97.1

TABLE 8.7.1.14

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION T L

ENVIRONMENT SALT FOG AT R T

CONDITION/HI	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
T73651	PLATE	0.03	18.30		13.1
T73651	PLATE	0.33	18.30		18.4
T73651	PLATE	0.33	18.30		28.5
T73652	FORGING	0.33	18.30		31.4
T76	SHEET	0.33	13.30		23.2
T76511	EXTRUSION	0.33	18.30		26.7

TABLE 8.7.1.15

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 7050

TEST CONDITIONS		ENVIRONMENT	L H A A T R I	FATIGUE CRACK GROWTH RATES							
SPECIMEN ORIENTATION	S L			PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	(MICRO IN/CYCLE)			
						2 5	5	10	20	50	100
T73651		PLATE	0 33	18 30							5 27
T76511		EXTRUSION	0 33	18 30							43 9

TABLE 8.7.1.16

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS

SPECIMEN ORIENTATION S-L

ENVIRONMENT H H A
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
				2 5 5 10 20 50 100	
17351	PLATE	0.33	1 00-20 00		11.9
173651	PLATE	0.33	18.30		14.9
176511	EXTRUSION	0.33	18.30		1.71 121

TABLE 8.7.1.17

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050

TEST CONDITIONS:

WETTING ORIENTATION S-U

ENVIRONMENT

SALT FOG
A T R I

CONDITIONS	PRODUCT FORM	STRESS RATIO	FRP (KSI)	DELTA K LEVELS (KSI 50RT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)
PLATE	PLATE	0.33	18.30	2.5 5 10 20 50 100	18.5
ROD	EXTRUSION	0.33	18.30		73.8

TABLE 8.7.2.1

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	THICK (IN)	TEMP (F)	SPECIMEN		DESIGN	CRACK LENGTH (IN)	K(IC) (IN)	2.9* K(IC)/TVS)**2 (IN)	K(IC) MEAN (KBI*SQRT IN)	STAN DEV	DATE	REFER
	FORM	7050					W	B								
T7E36	F		62.1	T-L	5.00	R.T.	1.500	0.750	NB	0.837	0.39	24.60		1972	85291	
			62.1		5.00		1.500	0.751	NB	0.863	0.57	29.80		1972	85291	
			62.1		5.00		1.500	0.750	NB	0.875	0.74	33.80		1972	85291	
			62.1		5.00		1.500	0.751	NB	0.837	0.48	27.20	28.9 / 3.9	1972	85291	
T7331	P		60.4	L-T	6.00	R.T.	4.000	2.000	CT	2.060	0.77	33.60		1977	AL001	
			60.4		2.00		4.000	2.000	CT	2.010	1.27	43.00		1977	AL001	
			60.4		6.00		4.000	2.000	CT	2.040	0.77	33.50		1977	AL001	
			60.4		2.00		4.000	2.000	CT	2.010	1.18	41.50		1977	AL001	
			60.4		2.00		4.000	2.000	CT	2.020	1.29	43.40		1977	AL001	
			60.4		6.00		4.000	2.000	CT	2.050	0.77	33.60		1977	AL001	
			61.1		2.00		4.000	2.000	CT	2.030	1.03	39.30		1977	AL001	
			61.1		2.00		4.000	2.000	CT	2.020	1.04	39.50		1977	AL001	
			61.1		2.00		4.000	2.000	CT	2.030	1.03	39.30		1977	AL001	
			62.2		6.00		4.000	2.000	CT	2.020	0.53	28.60		1977	AL001	
			62.2		6.00		4.000	2.000	CT	2.040	0.54	28.90		1977	AL001	
			62.2		6.00		4.000	2.000	CT	2.010	0.59	29.10		1977	AL001	
			63.2		5.12		4.000	2.000	CT	2.000	0.55	29.70		1977	AL001	
			63.2		5.12		4.000	1.980	CT	2.000	0.54	29.30		1977	AL001	
			63.7		5.00		4.000	2.000	CT	2.060	0.72	34.30		1977	AL001	
			63.7		3.00		4.000	2.000	CT	1.560	0.75	34.80		1977	AL001	
			63.7		3.00		3.000	1.500	CT	1.560	0.72	34.30		1977	AL001	
			63.7		4.00		4.000	2.000	CT	2.090	0.82	36.40		1977	AL001	
			63.7		4.00		4.000	2.000	CT	2.050	0.71	34.00		1977	AL001	
			63.7		4.00		4.000	2.000	CT	2.060	0.72	34.20		1977	AL001	
		63.7		5.00		4.000	2.000	CT	2.030	0.69	33.40		1977	AL001		
		63.7		5.00		4.000	2.000	CT	2.050	0.68	33.30		1977	AL001		
		63.7		4.00		4.000	2.000	CT	2.050	0.78	35.50		1977	AL001		
		63.7		4.00		4.000	2.000	CT	2.080	0.72	34.30		1977	AL001		
		63.7		3.00		3.000	1.500	CT	1.560	0.75	35.00		1977	AL001		
		63.7		4.00		4.000	2.000	CT	2.060	0.82	36.50		1977	AL001		
		63.9		3.00		3.000	1.500	CT	1.570	0.75	35.10		1977	AL001		
		63.9		3.00		3.000	1.500	CT	1.570	0.79	35.90		1977	AL001		
		63.9		3.00		3.000	1.500	CT	1.570	0.73	34.50		1977	AL001		
		69.8		1.00		2.000	1.004	CT	1.000	0.70	36.90	34.8 / 3.9	1974	88186		

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		---PRODUCT--- FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	---SPECIMEN--- WIDTH THICK DESIGN		CRACK LENGTH (IN)	K(1C) (IN)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER
	W	B														
T7351	P	6.00	R. T.	T-L	59.1	4.000	2.000	CT	2.080	0.63	29.60	1977	AL001			
					59.1	4.000	2.000	CT	2.090	0.64	30.30	1977	AL001			
					59.1	4.000	2.000	CT	2.070	0.64	29.80	1977	AL001			
					60.4	4.000	2.000	CT	2.060	0.82	34.50	1977	AL001			
					60.4	4.000	2.000	CT	2.070	0.82	34.50	1977	AL001			
					60.4	4.000	2.000	CT	2.060	0.87	35.60	1977	AL001			
					60.9	4.000	2.000	CT	2.050	0.47	26.30	1977	AL001			
					60.9	4.000	2.000	CT	2.080	0.48	26.60	1977	AL001			
					60.9	4.000	2.000	CT	2.070	0.71	32.40	1977	AL001			
					60.9	4.000	2.000	CT	2.070	0.72	32.60	1977	AL001			
					60.9	4.000	2.000	CT	2.050	0.70	32.20	1977	AL001			
					60.9	4.000	2.000	CT	2.050	0.48	26.70	1977	AL001			
					61.4	4.000	2.000	CT	2.020	0.41	24.90	1977	AL001			
					61.4	4.000	2.000	CT	2.050	0.41	25.00	1977	AL001			
					63.4	4.000	2.000	CT	2.080	0.54	29.40	1977	AL001			
					63.4	4.000	2.000	CT	2.090	0.57	30.80	1977	AL001			
					63.4	4.000	2.000	CT	2.100	0.58	30.50	1977	AL001			
					63.4	4.000	2.000	CT	2.040	0.54	29.40	1977	AL001			
					63.4	4.000	2.000	CT	2.090	0.51	28.60	1977	AL001			
					63.4	4.000	2.000	CT	2.100	0.58	30.60	1977	AL001			
63.7	4.000	2.000	CT	2.110	0.54	29.70	1977	AL001								
63.7	4.000	2.000	CT	2.120	0.53	29.40	1977	AL001								
63.7	3.000	1.500	CT	1.580	0.55	30.00	1977	AL001								
63.7	3.000	1.500	CT	1.580	0.55	29.90	1977	AL001								
63.7	3.000	1.500	CT	1.560	0.57	30.30	1977	AL001								
63.7	4.000	2.000	CT	2.100	0.53	29.40	1977	AL001								
64.2	3.000	1.500	CT	1.590	0.55	30.10	1977	AL001								
64.2	3.000	1.500	CT	1.590	0.56	30.40	1977	AL001								
64.2	3.000	1.500	CT	1.600	0.57	30.60	1977	AL001								
T7351	P	2.00	R. T.	S-L	55.3	1.500	0.750	CT	0.770	0.73	29.90	1977	AL001			
					55.3	1.500	0.750	CT	0.770	0.68	28.80	1977	AL001			
					55.3	1.500	0.750	CT	0.770	0.73	29.90	1977	AL001			
					55.6	1.500	0.750	CT	0.770	0.61	27.50	1977	AL001			
					55.6	1.500	0.750	CT	0.770	0.55	26.00	1977	AL001			
					55.6	1.500	0.750	CT	0.780	0.62	27.70	1977	AL001			
					56.3	3.000	1.500	CT	1.510	0.69	29.50	1977	AL001			
					56.3	3.000	1.500	CT	1.520	0.70	29.70	1977	AL001			
					56.3	3.000	1.500	CT	1.520	0.66	28.90	1977	AL001			
					56.3	3.000	1.500	CT	1.520	0.66	28.90	1977	AL001			

TABLE 8.7.2.1 (Cont)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	THICK (IN)	W	SPECIMEN		DESIGN LENGTH (IN)	CRACK LENGTH (IN)	K(1C)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER						
	FORM	THICK (IN)						THICK (IN)	A														
17351	P	6 00	R T.	S-L	6 00	3 000	1 500	CT	1 950	0 53	26 60	1977	AL001										
																		CT	1 530	0 50	26 10	1977	AL001
																		CT	1 500	0 53	26 70	1977	AL001
																		CT	1 500	0 47	25 90	1977	AL001
																		CT	1 520	0 50	26 20	1977	AL001
																		CT	1 530	0 49	26 00	1977	AL001
																		CT	1 540	0 60	28 90	1977	AL001
																		CT	1 520	0 58	28 20	1977	AL001
																		CT	1 530	0 56	27 90	1977	AL001
																		CT	1 530	0 58	28 50	1977	AL001
																		CT	1 530	0 55	27 70	1977	AL001
																		CT	1 530	0 62	29 40	1977	AL001
																		CT	1 540	0 59	29 20	1977	AL001
																		CT	1 530	0 59	29 10	1977	AL001
																		CT	1 540	0 58	28 90	1977	AL001
																		CT	1 280	0 51	27 20	1977	AL001
																		CT	1 280	0 50	27 00	1977	AL001
																		CT	1 270	0 53	28 30	1977	AL001
																		CT	1 270	0 48	27 00	1977	AL001
																		CT	1 280	0 53	28 40	1977	AL001
173511-HIGH/ PURITY	EB	1 50	R T.	L-T	1 50	2 500	1 250	CT	---	0 71	38 40	1980	HA001										
173511-HIGH/ PURITY	EB	1 50	R T.	T-L	1 50	2 500	1 250	CT	---	0 33	24 20	1980	HA001										
17352	F	5 00	82	L-T	5 00	3 000	1 502	CT	1 510	0 63	32 00	1973	86213										
17352	F	5 00	82	T-L	5 00	3 000	1 502	CT	1 580	0 22	18 50	1973	86213										
17352	F	6 00	R T.	S-L	6 00	4 000	2 000	CT	2 148	0 25	19 80	1973	86213										

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST TEMP (F)	SPECIMEN ORIENT	SPECIMEN		CRACK LENGTH (IN)	2.5* CRACK LENGTH (K(1C)/TVB)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER		
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)							DESIGN	
T7352	F	5.00	59.0	82	S-L	3.000	1.501	CT	1.574	0.34	21.90	21.9/	0.0	1973	86213
		5.00	59.0			3.000	1.502	CT	1.578	0.34	21.90	21.9/	0.0	1973	86213
T736	F	3.00	63.6	R.T.	L-T	1.996	1.000	CT	1.047	0.58	30.79	32.3/	2.3	1976	NC001
		3.00	63.6			1.998	1.001	CT	1.054	0.62	31.70			1976	NC001
		3.00	63.6			2.001	1.001	CT	1.049	0.59	31.11			1976	NC001
		-----	69.0			1.400	0.896	CT	0.674	0.66	39.70			1973	R9880
T736	F	6.00	61.9	82	L-T	3.000	1.499	CT	1.608	1.27	44.10			1973	86213
		7.10	63.5			2.000	0.999	CT	0.982	0.47	27.60			1973	86213
		7.10	65.1			2.000	1.001	CT	1.015	0.79	36.60			1973	86213
		4.25	69.3			3.000	1.499	CT	1.617	0.78	38.70			1973	86213
T736	F	6.00	61.4	R.T.	T-L	4.000	1.506	CT	-----	0.35	22.90			1973	91123
		3.00	62.2			2.003	1.001	CT	1.082	0.39	24.82			1976	NC001
		3.00	62.2			2.001	0.999	CT	1.054	0.35	23.44			1976	NC001
		3.00	62.2			1.996	0.999	CT	1.042	0.32	22.40			1976	NC001
T736	F	6.00	66.6	82	T-L	0.990	0.499	CT	0.912	0.22	19.70			1973	86213
T736	F	3.00	61.2	R.T.	S-T	2.000	1.000	CT	1.050	0.35	23.08			1976	NC001
		3.00	61.2			2.002	1.000	CT	1.060	0.41	24.84			1976	NC001
		3.00	61.2			1.999	1.000	CT	1.070	0.41	24.90			1976	NC001
T736	F	6.00	62.4	R.T.	S-L	4.000	1.509	CT	-----	0.79	24.60			1973	91123
		6.00	62.4			-----	2.000	CT	1.930	0.41	25.30			1973	86212
		6.00	62.4			4.000	1.509	CT	-----	0.37	24.00			1973	91123
		6.00	62.4			-----	2.000	CT	1.980	0.39	24.60			1973	86212
		6.00	62.4			4.000	1.509	CT	-----	0.41	25.30			1973	91123
		6.00	62.4			-----	2.000	CT	1.950	0.37	24.00			1973	86212
T736	F	7.10	63.4	82	S-L	2.000	0.999	CT	1.020	0.28	21.20			1973	86213
		7.10	63.4			2.000	0.999	CT	1.012	0.27	20.90			1973	86213
		7.10	64.2			2.000	0.999	CT	0.996	0.27	21.10			1973	86213
		6.00	64.2			2.000	0.999	CT	1.058	0.44	26.80			1973	86213
		6.00	64.2			2.000	1.000	CT	1.051	0.42	26.20			1973	86213
		0.60	64.5			1.500	0.635	CT	0.763	0.28	21.50			1973	86213

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	WIDTH (IN)	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(1C) (KSI*SQRT IN)	K(1C) MEAN (KSI)	STAN DEV (IN)	DATE	REFER	
	---PRODUCT---	7050												K(1C)
	FORM THICK (IN)	W												B
T736	F	---	R T	68.5	1.390	0.702	CT	0.687	0.47	29.80	0.5	1973	85880	
		---		68.5	1.400	0.699	CT	0.693	0.49	30.50	0.5	1973	85880	
T73651	P	1.00	65	75.7	2.000	1.005	CT	1.030	0.53	34.90	0.2	1974	88174	
		1.00		75.7	2.000	1.003	CT	1.039	0.54	35.20	0.2	1974	88174	
T73651	P	1.00	0	73.4	2.000	1.005	CT	1.028	0.61	36.40	1.1	1974	88174	
		1.00		73.4	1.990	1.003	CT	1.040	0.67	38.00	1.1	1974	88174	
T73651	P	5.25	R T	58.9	1.998	1.001	CT	0.992	0.71	31.40		1977	RA010	
		5.25		59.3	2.000	0.999	CT	0.963	0.67	30.90		1977	RA010	
		5.00		60.3	4.000	2.010	CT	2.040	0.57	28.70		1975	AL015	
		5.00		60.3	4.000	2.010	CT	2.050	0.57	28.90		1975	AL015	
		6.00		61.0	2.000	1.001	CT	0.972	0.57	29.20		1977	RA009	
		4.50		61.2	2.003	1.001	CT	0.962	0.57	29.29		1977	RA010	
		5.25		61.3	1.999	1.000	CT	0.939	0.57	29.40		1977	RA010	
		6.00		61.6	2.000	1.000	CT	0.966	0.76	34.00		1977	RA009	
		6.00		61.7	1.997	0.999	CT	1.006	0.59	30.10		1977	RA009	
		5.25		62.0	1.999	0.997	CT	0.962	0.59	30.10		1977	RA010	
		5.25		62.0	1.999	1.000	CT	0.950	0.56	29.40		1977	RA010	
		6.00		62.2	1.998	0.998	CT	0.950	0.60	30.40		1977	RA010	
		5.25		62.2	2.000	0.998	CT	1.015	0.52	28.50		1977	RA009	
		5.25		62.3	2.000	0.999	CT	0.993	0.55	29.29		1977	RA010	
		5.25		62.3	2.000	0.999	CT	0.980	0.55	29.40		1977	RA010	
		6.00		62.5	2.003	1.001	CT	0.989	0.50	28.29		1977	RA010	
		6.00		62.7	1.997	1.000	CT	0.959	0.50	28.20		1977	RA009	
		4.50		62.9	1.999	1.001	CT	0.981	0.51	28.40		1977	RA009	
		5.25		63.1	1.998	0.999	CT	1.492	0.67	32.59		1978	RA008	
		6.00		63.3	2.001	1.000	CT	0.973	0.54	29.40		1977	RA010	
		6.00		63.4	1.998	1.001	CT	0.963	0.57	30.29		1977	RA009	
		5.25		63.5	1.999	0.997	CT	0.964	0.48	28.00		1977	RA009	
		4.50		63.6	3.002	1.001	CT	0.993	0.54	29.70		1977	RA010	
		5.00		63.6	2.001	1.001	CT	0.979	0.50	28.60		1977	RA009	
		5.00		63.7	4.000	2.000	CT	1.530	0.54	29.70		1978	RA008	
		5.00		63.7	4.000	2.000	CT	2.090	0.40	25.70		1975	AL015	
		6.00		63.8	2.000	1.000	CT	2.080	0.40	25.50		1975	AL015	
								0.975	0.76	35.30		1977	RA009	

TABLE 8.7.2.1 (Con't)

CONDITION	---PRODUCT--- FORM THICK (IN)		TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM		---SPECIMEN--- WIDTH THICK (IN)		CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	K(1C) STAN DEV (IN)	DATE	REFER
	P	H				A	B								
T73691	5.25	63.8	R.T.	L-T	63.8	1.999	0.999	0.972	0.53	0.972	0.53	29.40		1977	RA010
	6.00	63.8			63.8	1.999	1.001	0.971	0.48	0.971	0.48	28.20		1977	RA009
	5.25	63.9			63.9	1.999	1.000	0.954	0.48	0.954	0.48	28.10		1977	RA010
	4.50	63.9			63.9	2.999	1.498	1.531	0.46	1.531	0.46	27.50		1978	RA008
	2.75	63.9			63.9	2.003	0.999	1.000	0.53	1.000	0.53	29.60		1977	RA010
	5.25	64.0			64.0	2.003	1.000	0.965	0.49	0.965	0.49	28.60		1977	RA010
	4.00	64.2			64.2	1.999	1.001	1.008	0.46	1.008	0.46	27.79		1977	RA010
	4.00	64.4			64.4	1.998	0.997	1.052	0.80	1.052	0.80	36.59		1977	RA009
	4.00	64.7			64.7	1.998	1.001	1.010	0.57	1.010	0.57	31.10		1977	RA009
	4.00	65.0			65.0	3.000	1.502	1.543	0.55	1.543	0.55	30.40		1973	89836
	4.00	65.0			65.0	3.000	1.499	1.569	0.41	1.569	0.41	26.30		1973	89836
	4.00	65.4			65.4	1.998	0.997	0.980	0.78	0.980	0.78	36.70		1977	RA009
	6.00	65.4			65.4	2.000	1.001	1.040	0.60	1.040	0.60	32.30		1977	RA009
	4.00	65.9			65.9	1.998	0.998	1.001	0.59	1.001	0.59	32.09		1977	RA009
	3.00	66.9			66.9	2.000	1.000	1.018	0.42	1.018	0.42	27.30		1973	86429
	3.00	66.9			66.9	1.990	1.000	1.014	0.44	1.014	0.44	28.20		1973	86429
	3.00	66.9			66.9	2.010	1.000	1.010	0.38	1.010	0.38	26.10		1973	86429
	4.00	67.2			67.2	1.998	0.977	1.091	0.54	1.091	0.54	31.50		1977	RA009
	4.00	67.2			67.2	2.490	1.248	1.234	0.64	1.234	0.64	34.20		1972	84363
	4.00	67.2			67.2	2.490	1.255	1.264	0.67	1.264	0.67	35.00		1972	84363
	4.00	67.2			67.2	1.998	0.998	1.003	0.73	1.003	0.73	36.50		1977	RA009
	4.00	67.2			67.2	2.490	1.250	1.279	0.74	1.279	0.74	36.80		1972	84363
	3.50	67.4			67.4	3.001	1.500	1.455	0.59	1.455	0.59	33.00		1978	RA008
	3.50	67.8			67.8	3.000	1.496	1.455	0.46	1.455	0.46	29.20		1978	RA008
	4.00	67.8			67.8	1.997	0.996	1.009	0.51	1.009	0.51	30.79		1977	RA009
	2.00	67.8			67.8	1.998	0.994	0.998	0.59	0.998	0.59	33.09		1977	RA009
	3.50	68.3			68.3	1.997	0.998	1.091	0.63	1.091	0.63	34.50		1977	RA009
	3.50	68.5			68.5	1.998	0.977	1.042	0.56	1.042	0.56	32.70		1977	RA009
	4.00	68.6			68.6	2.001	1.001	0.941	0.58	0.941	0.58	33.09		1977	RA009
	3.15	69.0			69.0	2.001	1.007	1.009	0.34	1.009	0.34	25.80		1976	NC001
	3.15	69.0			69.0	2.002	1.007	0.993	0.34	0.993	0.34	25.72		1976	NC001
	3.15	69.0			69.0	2.002	1.007	1.005	0.34	1.005	0.34	25.54		1976	NC001
	2.50	69.1			69.1	2.000	0.999	1.027	0.45	1.027	0.45	29.60		1978	RA010
	3.00	69.6			69.6	2.003	1.001	0.958	0.65	0.958	0.65	39.70		1977	RA010
	1.00	70.0			70.0	2.000	1.004	1.034	0.69	1.034	0.69	36.80		1974	88174
	1.00	70.0			70.0	2.000	0.976	---	0.66	---	0.66	36.00		1982	NC003
	1.00	70.0			70.0	2.000	1.003	1.027	0.71	1.027	0.71	37.40		1974	88174
	1.00	70.0			70.0	2.000	1.003	1.035	0.65	1.035	0.65	35.70		1974	88174
	1.00	70.0			70.0	2.000	0.976	---	0.66	---	0.66	36.00		1982	NC003

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	SPECIMEN		CRACK LENGTH (IN)	2.5* K(KIC)/TYS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	K(KIC) STAN DEV (KSI*SQRT IN)	DATE	REFER																				
	PRODUCT FORM	THICK (IN)			WIDTH (IN)	THICK (IN)							DESIGN																			
173651	P	2.50	R T	L-T	70.2	2.000	0.999	CT	1.076	0.40	28.29	1978	RA010																			
												1.00	2.000	1.003	CT	1.009	0.64	35.70	1973	86213												
												1.00	2.000	0.998	CT	1.028	0.60	34.70	1973	86213												
												1.00	2.000	0.998	CT	1.034	0.64	35.70	1973	86213												
												2.00	1.998	0.992	CT	1.034	0.48	31.50	1977	RA009												
												1.00	2.000	1.000	NB	0.964	0.62	36.90	1973	86493												
												1.00	2.000	1.000	NB	0.992	0.61	36.40	1973	86493												
												1.00	2.000	1.000	NB	1.010	0.70	39.10	1973	86493												
												1.00	2.000	1.000	NB	1.010	0.70	39.10	1973	86493												
												1.00	2.000	1.000	NB	0.964	0.65	37.70	1973	86493												
												1.00	2.000	1.000	NB	0.992	0.61	36.40	1973	86493												
												1.00	2.000	1.000	NB	1.000	0.69	37.70	1973	86493												
												1.00	2.000	1.000	NB	0.990	0.66	37.80	1973	86493												
												1.00	2.000	1.000	NB	1.000	0.65	37.70	1973	86493												
												1.00	2.000	1.000	NB	1.000	0.65	37.70	1973	86493												
173651	P	4.00	82	L-T	63.7	4.000	1.998	CT	2.099	0.64	32.30	1973	86213																			
												4.00	4.000	1.998	CT	2.071	0.67	32.90	1973	86213												
												4.00	4.000	1.996	CT	2.145	0.55	30.70	1973	86213												
												4.00	3.990	1.999	CT	2.155	0.57	31.20	1973	86213												
												2.00	4.000	1.997	CT	2.115	0.75	36.10	1973	86213												
												2.00	4.000	1.997	CT	2.138	0.77	36.60	1973	86213												
												2.00	4.000	1.996	CT	2.132	0.70	35.40	1973	86213												
												2.00	4.000	1.997	CT	2.136	0.71	35.70	1973	86213												
												1.00	2.000	0.999	CT	1.003	0.58	31.50	1973	86213												
												1.00	2.000	0.998	CT	1.020	0.60	32.00	1973	86213												
												173651	P	1.00	250	L-T	64.4	1.990	1.002	CT	1.034	0.89	37.50	1974	88174							
																								1.00	2.000	1.004	CT	1.036	0.83	37.10	1974	88174
																								1.00	2.000	1.006	CT	1.048	0.41	30.40	1974	88174
												173651	P	1.00	65	T-L	75.0	2.000	1.005	CT	1.027	0.40	30.00	1974	88174							
																								1.00	2.000	1.005	CT	1.027	0.40	30.00	1974	88174
173651	P	1.00	0	T-L	72.7	2.000	1.005	CT	1.037	0.47	31.60	1974	88174																			

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEMP (F)	SPECIMEN		DESIGN LENGTH (IN)	CRACK LENGTH (IN)	K(1C) 2.5* (IN)	K(1C)/TYS)**2 (IN)	K(1C) MEAN (IN)	STAN DEV	DATE	REFER
	FORM	THICK (IN)				WIDTH (IN)	THICK (IN)								
T73651	P	1.00	72.7	0	T-L	2.000	1.004	CT	1.024	0.46	31.30	31.30		1974	BB174
		1.00	72.7			2.000	1.004	CT	1.028	0.46	31.20	31.20		1974	BB174
		1.00	72.7			2.000	1.007	CT	1.030	0.46	31.20	31.3/	0.2	1974	BB174
T73651	P	5.25	59.0	R.T.	T-L	1.999	1.001	CT	0.969	0.40	23.60	23.60		1977	RA010
		5.00	59.1			4.000	2.010	CT	2.130	0.47	25.70	25.70		1975	AL015
		5.00	59.1			4.000	2.000	CT	2.100	0.43	24.50	24.50		1975	AL015
		4.50	59.2			1.999	1.002	CT	0.983	0.59	28.90	28.90		1977	RA010
		5.25	59.9			2.000	0.998	CT	0.970	0.35	22.50	22.50		1977	RA010
		5.00	60.1			4.000	2.000	CT	2.130	0.41	24.40	24.40		1975	AL015
		6.00	60.1			2.002	1.002	CT	0.986	0.59	29.40	29.40		1977	RA009
		5.00	60.1			4.000	2.010	CT	2.080	0.43	24.50	24.50		1975	AL015
		5.25	60.2			2.003	1.000	CT	1.001	0.36	23.00	23.00		1977	RA010
		6.00	60.4			1.998	1.001	CT	1.018	0.56	28.60	28.60		1977	RA009
		5.25	60.5			1.999	0.999	CT	0.979	0.34	22.40	22.40		1977	RA010
		6.00	60.5			1.998	0.999	CT	1.030	0.55	28.50	28.50		1977	RA009
		6.00	60.6			1.997	0.999	CT	0.991	0.46	26.20	26.20		1977	RA009
		6.00	60.7			2.001	1.001	CT	0.979	0.54	28.40	28.40		1977	RA010
		5.25	61.1			1.999	0.998	CT	0.996	0.33	22.20	22.20		1977	RA010
		6.00	61.1			1.998	1.000	CT	1.027	0.53	28.10	28.10		1977	RA009
		6.00	61.4			1.999	1.000	CT	0.988	0.71	32.80	32.80		1977	RA009
	5.25	61.4			2.003	1.000	CT	1.015	0.43	25.70	25.70		1977	RA010	
	5.25	61.6			2.000	1.000	CT	0.996	0.33	22.70	22.70		1977	RA010	
	4.50	61.7			3.000	1.500	CT	1.483	0.77	34.30	34.30		1978	RA008	
	6.00	61.8			2.000	1.000	CT	0.968	0.50	27.70	27.70		1977	RA009	
	4.00	61.8			1.998	0.997	CT	1.006	0.60	30.59	30.59		1977	RA009	
	6.00	61.8			2.000	1.001	CT	0.987	0.50	27.79	27.79		1977	RA009	
	4.00	62.0			1.998	0.998	CT	0.994	0.57	29.70	29.70		1977	RA009	
	5.25	62.1			2.000	1.000	CT	1.001	0.39	23.90	23.90		1977	RA010	
	5.25	62.3			2.003	1.000	CT	0.997	0.59	24.70	24.70		1977	RA010	
	5.25	62.4			2.001	0.999	CT	0.994	0.31	22.20	22.20		1977	RA010	
	5.25	62.5			2.003	1.002	CT	1.006	0.30	22.00	22.00		1977	RA010	
	4.00	62.6			1.998	0.998	CT	0.990	0.48	27.50	27.50		1977	RA009	
	6.00	62.7			1.999	1.001	CT	0.968	0.50	28.20	28.20		1977	RA009	
	6.00	62.7			2.001	1.001	CT	0.971	0.48	27.60	27.60		1977	RA009	
	6.00	62.9			2.002	1.001	CT	0.955	0.49	27.90	27.90		1977	RA009	
	4.00	62.9			1.999	1.000	CT	1.049	0.33	22.90	22.90		1977	RA010	
	4.00	62.9			1.999	1.000	CT	1.049	0.33	22.90	22.90		1977	RA010	
	4.00	63.2			1.997	1.000	CT	1.007	0.50	28.59	28.59		1977	RA009	

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN		DESIGN THICK (IN)	CRACK LENGTH (IN)	K(1C)		DATE	REFER	
	FORM	THICK (IN)		WIDTH (IN)	THICK (IN)			2.5* K(1C)/TVS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)			STAN DEV (IN)
173651	P	5 25	63.2	1.999	1.000	CT	0.989	0.30	22.10	1977	RA010	
		2 75	63.4	2.003	0.999	CT	1.025	0.43	26.29	1977	RA010	
		5 25	63.7	1.998	1.001	CT	0.993	0.28	31.40	1977	RA010	
		6 00	63.9	1.999	1.000	CT	0.978	0.77	35.50	1977	RA009	
		4 00	64.1	1.998	0.999	CT	0.964	0.65	32.90	1977	RA009	
		5 25	64.3	3.002	1.490	CT	1.480	0.62	32.20	1978	RA008	
		4 50	64.6	2.000	1.001	CT	0.961	0.51	29.40	1977	RA009	
		6 00	64.6	2.001	0.999	CT	0.958	0.46	28.00	1977	RA009	
		6 00	64.6	2.000	1.000	CT	0.964	0.51	29.40	1977	RA009	
		4 00	65.0	2.990	1.502	CT	1.555	0.40	26.10	1973	B5836	
		4 00	65.0	3.000	1.499	CT	1.564	0.42	26.70	1973	B5836	
		6 00	65.0	1.997	0.999	CT	1.032	0.42	36.90	1977	RA009	
		4 00	65.0	3.000	1.500	CT	1.540	0.54	30.30	1973	B5836	
		5 25	65.3	1.999	0.997	CT	0.969	0.27	21.50	1977	RA010	
		4 00	65.5	1.997	0.999	CT	1.005	0.41	26.79	1977	RA009	
		3 50	66.1	1.998	0.998	CT	1.050	0.44	28.00	1977	RA009	
		3 50	66.2	3.000	1.499	CT	1.494	0.45	28.10	1978	RA008	
		3 50	67.4	1.997	0.996	CT	1.032	0.44	28.40	1977	RA009	
		3 50	67.6	3.000	1.501	CT	1.541	0.38	26.60	1978	RA008	
		3 50	67.6	1.998	0.999	CT	1.073	0.35	25.40	1977	RA009	
		2 00	68.2	1.998	0.994	CT	1.009	0.50	30.70	1977	RA009	
		3 15	68.9	2.001	1.007	CT	1.019	0.35	25.91	1976	NC001	
		3 15	68.9	2.001	1.007	CT	1.012	0.37	26.60	1976	NC001	
		3 15	68.9	2.001	1.007	CT	1.031	0.31	24.59	1976	NC001	
		3 00	68.9	2.003	1.000	CT	1.015	0.52	31.60	1977	RA010	
		2 00	69.2	1.998	0.994	CT	1.030	0.41	28.29	1977	RA009	
		2 50	69.7	2.001	0.999	CT	1.039	0.26	22.50	1978	RA010	
		1 00	69.8	2.000	0.999	CT	1.035	0.54	32.40	1973	B6213	
		1 00	69.8	2.000	0.998	CT	1.032	0.49	31.00	1973	B6213	
		1 00	70.0	2.000	1.003	CT	1.032	0.49	31.00	1973	B6213	
		1 00	70.0	2.000	1.003	CT	1.030	0.52	31.80	1973	B6213	
		2 50	70.7	2.000	0.999	CT	1.094	0.35	26.79	1978	RA010	
		1 00	72.2	2.000	1.004	CT	1.036	0.50	32.40	1974	B8174	
		1 00	72.2	2.000	1.005	CT	1.038	0.49	32.10	1974	B8174	
		1 00	72.2	2.000	1.005	CT	1.030	0.50	32.30	1974	B8174	
		1 00	72.5	2.000	1.000	NB	0.963	0.65	36.90	1973	B6493	
		1 00	72.5	2.000	1.000	NB	0.963	0.65	36.90	1973	B6493	
		1 00	72.5	2.000	1.000	NB	0.977	0.64	36.70	1973	B6493	

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		YIELD STRENGTH (KSI)	SPECIMEN THICKNESS (IN)	DESIGN	CRACK LENGTH (IN)	2.5* (K(KIC)/TVS)**2 (IN)	K(KIC) MEAN (KSI*SQRT IN)	STAN DEV (IN)	DATE	REFER	
	PRODUCT FORM	TEST TEMP (F)										
T73651	P	R T	T-L	1 00	2 000	NB	0 997	0 64	36 80	1973	86493	
				1 00	2 000	NB	1 000	0 67	37 70	1973	86493	
				1 00	2 000	NB	1 000	0 68	37 70	1973	86493	
				1 00	2 000	NB	0 990	0 63	36 30	1973	86493	
				1 00	2 000	NB	0 978	0 68	37 80	1973	86493	
				1 00	2 000	NB	0 978	0 68	37 80	1973	86493	
				1 00	2 000	NB	0 990	0 63	36 30	1973	86493	
				1 00	2 000	NB	0 963	0 65	36 90	1973	86493	
				1 00	2 000	NB	0 963	0 65	36 90	28 7 / 4 7	1973	86493
				1 00	2 000	NB	0 963	0 65	36 90	28 7 / 4 7	1973	86493
T73651	P	82	T-L	4 00	4 000	CT	2 167	0 47	27 30	1973	86213	
				4 00	4 000	CT	2 126	0 46	27 10	1973	86213	
				4 00	3 990	CT	2 109	0 43	26 60	1973	86213	
				4 00	4 000	CT	2 124	0 41	26 20	1973	86213	
				2 00	4 000	CT	2 166	0 50	29 40	1973	86213	
				2 00	4 000	CT	2 156	0 49	29 20	1973	86213	
				2 00	4 000	CT	2 130	0 45	28 50	1973	86213	
				2 00	4 000	CT	2 123	0 46	28 80	27 9 / 1 2	1973	86213
				1 00	2 000	CT	0 994	0 40	26 00	1973	86213	
				0 50	1 000	CT	0 974	0 39	25 90	1973	86213	
0 50	1 000	CT	0 501	0 42	27 50	1973	86213					
0 50	1 000	CT	0 511	0 40	26 80	26 6 / 0 8	1973	86213				
T73651	P	R T	S-T	6 00	2 000	CT	1 023	0 52	25 60	1977	RA009	
				6 00	1 998	CT	1 077	0 60	27 60	1977	RA009	
				6 00	1 999	CT	1 029	0 49	25 10	1977	RA009	
				6 00	2 000	CT	1 035	0 44	24 00	1977	RA009	
				6 00	2 001	CT	1 001	0 42	23 40	1977	RA009	
				6 00	2 000	CT	0 947	0 53	26 40	1977	RA009	
				6 00	2 001	CT	1 033	0 44	24 40	1977	RA009	
				6 00	1 997	CT	0 993	0 36	22 10	1977	RA009	
				6 00	1 997	CT	0 994	0 49	25 80	1977	RA009	
				6 00	1 996	CT	1 035	0 59	28 40	1977	RA009	
6 00	2 000	CT	1 017	0 51	26 50	1977	RA009					
6 00	1 998	CT	0 975	0 35	22 10	1977	RA009					
6 00	2 000	CT	1 034	0 42	24 20	1977	RA009					
6 00	2 001	CT	1 066	0 44	24 79	1977	RA009					
6 00	2 001	CT	1 028	0 37	23 00	1977	RA009					

TABLE 8.7.2.1.1 (Con't)

CONDITION	ALUMINUM	7050	K(1C)	PRODUCT FORM	THICK (IN)	TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	SPECIMEN DESIGN		CRACK LENGTH (IN)	2.5* K(1C)/TYS)**2 (IN)	K(1C) MEAN (K(1C)*SORT IN)	STAIN DEV	DATE	REFER		
									W (IN)	B (IN)								
173651	P	6 00	1.997	0.997	CT	0.996	0.38	23 50	1977	RA009								
		6 00	2.000	1.000	CT	1.020	0.36	23 10	1977	RA009								
		6 00	2.000	1.000	CT	1.048	0.40	24 50	1977	RA009								
		4 00	1.998	0.998	CT	0.976	0.38	23 90	1977	RA009								
		4 00	1.998	0.999	CT	0.996	0.46	26 40	1977	RA009								
		4 00	1.998	0.996	CT	0.976	0.45	26 20	1977	RA009								
		4 00	1.998	0.996	CT	0.963	0.36	23 90	1977	RA009								
		4 00	1.998	0.994	CT	1.026	0.31	22 79	1977	RA009								
		3 50	1.998	0.999	CT	0.938	0.32	23 00	1978	RA008								
		3 15	2.002	1.007	CT	1.020	0.24	20 33	1976	NC001								
		3 15	2.002	1.007	CT	1.038	0.30	22 52	1976	NC001								
		3 50	2.002	1.007	CT	1.066	0.29	20 73	1976	NC001								
		4 00	2.001	0.999	CT	1.056	0.28	21 90	1978	RA010								
		4 00	1.998	0.998	CT	0.979	0.27	21 79	1977	RA009								
		3 50	2.000	0.998	CT	0.956	0.31	23 29	1978	RA008								
		2 50	2.001	0.999	CT	1.028	0.30	23 00	1978	RA010								
		3 50	1.997	0.997	CT	1.034	0.32	23 90	1977	RA009								
		3 50	1.998	0.998	CT	1.050	0.31	23 60	1977	RA009								
		3 50	1.997	0.995	CT	1.018	0.28	22 90	23 9/	1 9	1977	RA009						
173651	P	5 25	1.999	0.999	CT	0.924	0.43	22 90	1977	RA010								
		4 50	2.003	1.000	CT	1.033	0.46	24 29	1977	RA010								
		2 75	2.003	0.999	CT	0.982	0.44	23 79	1977	RA010								
		5 25	2.003	1.000	CT	0.950	0.39	22 60	1977	RA010								
		5 00	4.000	2.010	CT	2.070	0.47	24 70	1975	AL015								
		5 25	2.000	0.998	CT	1.005	0.40	22 79	1977	RA010								
		5 25	1.999	1.000	CT	0.933	0.42	23 40	1977	RA010								
		5 25	1.999	0.998	CT	0.944	0.41	23 20	1977	RA010								
		5 25	1.999	0.999	CT	0.941	0.36	21 90	1977	RA010								
		5 25	2.003	1.001	CT	0.946	0.40	23 29	1977	RA010								
		5 25	2.003	1.001	CT	0.990	0.42	23 70	1977	RA010								
		5 25	2.003	1.000	CT	0.959	0.36	22 29	1977	RA010								
		5 25	2.000	0.999	CT	0.938	0.42	23 90	1977	RA010								
		5 25	2.003	0.970	CT	0.969	0.41	23 70	1977	RA010								
		5 25	1.999	0.997	CT	0.968	0.43	24 10	1977	RA010								
		5 25	2.000	1.000	CT	0.955	0.38	23 10	1977	RA010								
		5 25	2.000	0.998	CT	0.966	0.37	22 79	1977	RA010								
		5 00	4.000	2.000	CT	2.030	0.37	22 80	1975	AL015								

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINIUM		YIELD STRENGTH (KSI)	TEST SPECIMEN ORIENT	TEST TEMP (F)	SPECIMEN			W	M	W	THICK (IN)	DESIGN	CRACK LENGTH (IN)	K(1C)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER
	PRODUCT FORM	THICK (IN)				THICK (IN)	THICK (IN)													
	A	B				A														
173651	P	5 00	R T	5-L	59.3	4.000	2.000	CT	2.030	0.37	22.90	1975	AL015							
		5 25			59.6	1.999	1.002	CT	0.952	0.32	21.50	1977	RA010							
		4 50			60.3	3.002	1.497	CT	1.550	0.44	25.29	1978	RA008							
		5 25			60.6	1.998	0.999	CT	0.952	0.33	22.29	1977	RA010							
		5 25			61.7	1.997	0.999	CT	0.990	0.28	20.79	1977	RA010							
		4 00			61.7	2.003	0.999	CT	0.974	0.31	21.90	1977	RA010							
		5 25			62.0	1.999	0.998	CT	0.937	0.27	21.40	1977	RA010							
		4 00			63.7	2.980	1.500	CT	1.469	0.37	24.50	1973	86213							
		4 00			63.7	2.990	1.500	CT	1.507	0.43	26.40	1973	86213							
		3 00			64.0	1.990	1.000	CT	1.029	0.34	23.90	1973	86429							
		3 00			64.0	2.000	1.000	CT	1.029	0.31	22.70	1973	86429							
		3 00			64.0	1.990	1.000	CT	1.034	0.31	22.60	1973	86429							
		4 00			65.0	3.000	1.502	CT	1.519	0.37	25.10	1973	85836							
		4 00			65.0	3.000	1.501	CT	1.550	0.36	24.80	1973	85836							
		4 00			65.0	3.000	1.500	CT	1.531	0.39	25.80	1973	85836							
		3 00			66.4	2.003	1.001	CT	0.970	0.45	28.20	23 5/ 1 9	1977	RA010						
		173651	P	2 00		81	64.2	1.490	0.749	CT	0.760	0.40	25.60	1973	86213					
2 00					64.2	1.500	0.749	CT	0.743	0.40	25.60	25 6/ 0 0	1973	86213						
173651	P	4 00		84	59.7	3.000	1.498	CT	1.503	0.39	23.70	1973	86213							
		2 00			61.5	1.490	0.748	CT	0.695	0.33	22.40	23 1/ 0 9	1973	86213						
173652	F	3 50	R T	L-T	61.1	3.000	1.500	CT	1.630	0.74	33.30	1975	AL015							
		3 50			61.1	3.000	1.500	CT	1.540	0.79	34.40	1975	AL015							
		5 50			63.0	3.000	1.500	CT	1.510	0.63	31.50	1975	AL015							
		4 50			63.2	3.000	1.500	CT	1.500	0.59	30.60	1975	AL015							
		5 50			68.8	3.000	1.510	CT	1.510	0.60	30.90	264	AL 015							
		5 50			68.8	3.000	1.500	CT	1.520	0.56	32.50	1975	AL015							
		3 50			70.0	3.000	1.500	CT	1.530	0.61	34.00	1975	AL015							
		3 50			70.0	3.000	1.500	CT	1.560	0.47	30.20	1975	AL015							
		3 50			70.0	3.000	1.500	CT	1.530	0.46	30.10	1975	AL015							
		---			72.0	3.000	1.500	CT	1.670	0.38	28.00	1975	AL015							
		---			72.0	3.000	1.500	CT	1.640	0.33	26.20	31 1/ 2 5	1975	AL015						
		173652	F	7 50		82	60.9	3.000	1.499	CT	1.458	0.77	33.70	1973	86213					
				4 50			62.1	3.000	1.497	CT	1.531	0.92	37.70	1973	86213					

TABLE 8.7.2.1 (Con't)

CONDITION	--PRODUCT-- FORM THICK (IN)		TEST TEMP (F)	SPECIMEN ORIENT	YIELD STRENGTH (KSI)	ALUMINUM 7050		K(1C)		CRACK LENGTH (IN)	2.5* (K(1C)/TYS)**2 (IN)	K(1C) MEAN DEV (KSI*SQRT IN)	K(1C) STAN DEV	DATE	REFER	
	W	B				WIDTH (IN)	THICK (IN)	A								
T73652	F	4 50 2 50	82	L-T	62.1 67.3	3.000 3.000	1.498 1.499	CT CT	1.554 1.465	0.82 0.47	35.50 29.30	34.1/	3.6	1973	86213 86213	
	T73652	F	4 50	R.T.	T-L	59.3	3.000	1.510	CT	1.540	0.31	20.90			1975	AL015
4 50					59.3	3.000	1.510	CT	1.560	0.32	21.20			1975	AL015	
7 50					60.7	3.000	1.500	CT	1.560	0.23	18.40			1975	AL015	
3 50					60.8	3.000	1.500	CT	1.530	0.32	21.90			1975	AL015	
4 50					60.8	3.000	1.500	CT	1.580	0.25	19.10			1975	AL015	
3 50					60.8	3.000	1.500	CT	1.560	0.32	21.70			1975	AL015	
4 50					60.8	3.000	1.500	CT	1.560	0.27	20.00			1975	AL015	
5 50					62.6	3.000	1.500	CT	1.520	0.29	21.30			1975	AL015	
5 50					62.6	3.000	1.500	CT	1.540	0.29	21.30			1975	AL015	
3 50					66.0	3.000	1.500	CT	1.580	0.30	22.70			1975	AL015	
3 50					66.0	3.000	1.500	CT	1.540	0.29	22.50			1975	AL015	
5 50					66.2	3.000	1.500	CT	1.560	0.21	19.00			1975	AL015	
5 50					66.2	3.000	1.500	CT	1.580	0.22	19.70	20.7/	1.4		1975	AL015
T73652		F	4 50 2 50	82	T-L	60.2 65.5	3.000 3.000	1.499 1.500	CT CT	1.556 1.580	0.33 0.40	21.90 26.20			1973	86213 86213
	2 50				65.5	3.000	1.498	CT	1.604	0.43	27.20	25.1/	2.8	1973	86213	
T73652	F	3 50	R.T.	S-L	56.5	3.000	1.500	CT	1.540	0.29	19.40			1975	AL015	
	3 50				56.5	3.000	1.500	CT	1.530	0.29	19.30			1975	AL015	
	5 50				57.1	3.000	1.500	CT	1.540	0.29	19.30			1975	AL015	
	5 50				57.1	3.000	1.500	CT	1.500	0.27	18.90			1975	AL015	
	4 50				57.3	3.000	1.500	CT	1.560	0.25	18.10			1975	AL015	
	4 50				57.3	3.000	1.500	CT	1.560	0.26	18.60			1975	AL015	
	7 50				57.8	3.000	1.500	CT	1.500	0.34	18.00			1975	AL015	
	7 50				58.1	3.000	1.500	CT	1.520	0.24	21.40			1975	AL015	
	4 50				61.1	3.000	1.500	CT	1.540	0.20	20.70			1975	AL015	
	4 50				61.1	3.000	1.500	CT	1.530	0.19	16.80			1975	AL015	
	5 50				62.1	3.000	1.500	CT	1.530	0.26	20.20			1975	AL015	
	5 50				62.1	3.000	1.500	CT	1.560	0.23	19.00			1975	AL015	
	3 50				64.4	3.000	1.500	CT	1.610	0.27	21.10			1975	AL015	
	3 50				64.4	3.000	1.500	CT	1.570	0.28	21.40			1975	AL015	
---				67.6	1.500	0.750	CT	0.770	0.19	18.60			1975	AL015		
---				67.6	1.500	0.750	CT	0.760	0.19	18.70	19.2/	1.4		1975	AL015	

TABLE 8.7.2.1 (Con't)

CONDITION	ALUMINUM		TEST SPECIMEN ORIENT	YIELD STRENGTH (KSI)	SPECIMEN		CRACK LENGTH (IN)	2.5* (K(IC)/TYS)**2 (IN)	K(IC) MEAN (KSI*SQRT IN)	STAN DEV	DATE	REFER		
	FORM	THICK (IN)			WIDTH (IN)	THICK (IN)							DESIGN	K(IC)
173652	F	2.50	82	61.3	2.000	0.999	CT	0.986	19.90	19.20	1973	86213		
		2.50		61.3	2.000	0.999	CT	0.997	18.50	1.0	1973	86213		
17451	P	1.00	R.T.	78.3	2.500	1.004	CT	1.280	30.70		1973	86574		
		1.00		78.3	2.500	1.004	CT	1.279	31.10		1973	86574		
		1.00		78.3	2.500	1.003	CT	1.274	30.60	30.8/	0.3	1973	86574	
176511	F	2.00	R.T.	71.4	1.500	0.749	CT	0.735	24.30		1973	86213		

TABLE 8.7.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.1 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7050
CONDITION: T6
ENVIRONMENT: R.T., L.H.A

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.33			
DELTA K MIN	A:	6.13	2.91		
	B:				
	C:				
	D:				
		7.00	4.01		
		8.00	6.16		
		9.00	8.98		
		10.00	11.9		
DELTA K MAX		13.00	21.8		
		16.00	41.8		
		20.00	114.		
		25.00	280.		
	A:	25.27	287.		
	B:				
C:					
D:					

ROOT MEAN SQUARE 9.08
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 4
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T6
 FORM: 0.18" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 FREQUENCY: 13.30 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 75.0 KSI
 ULT. STRENGTH: 83.2 KSI
 SPECIMEN THK: 0.177- 0.179"
 SPECIMEN WIDTH: 3.999- 4.000"
 REFERENCES: 86213

ALUM.
 ALLOY

7050

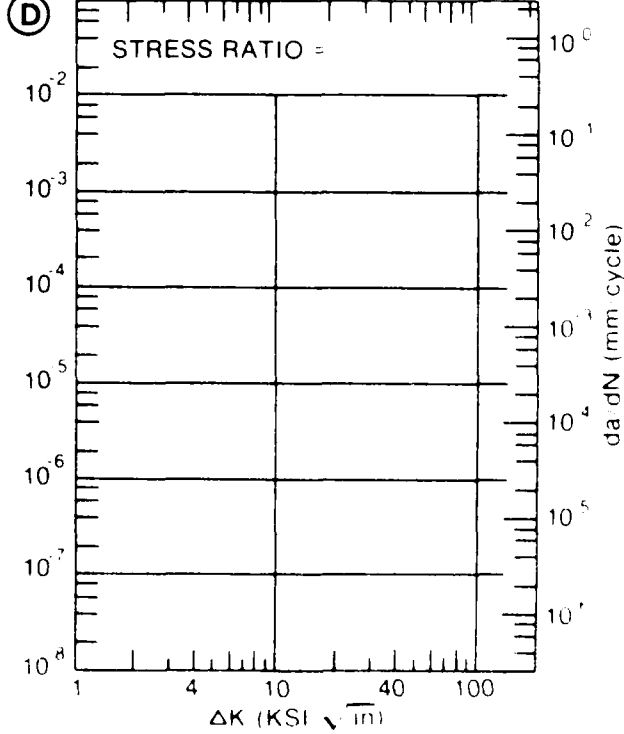
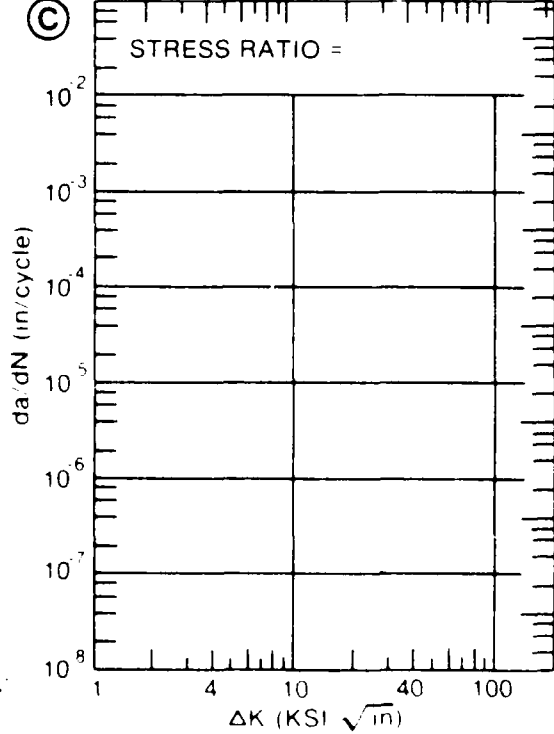
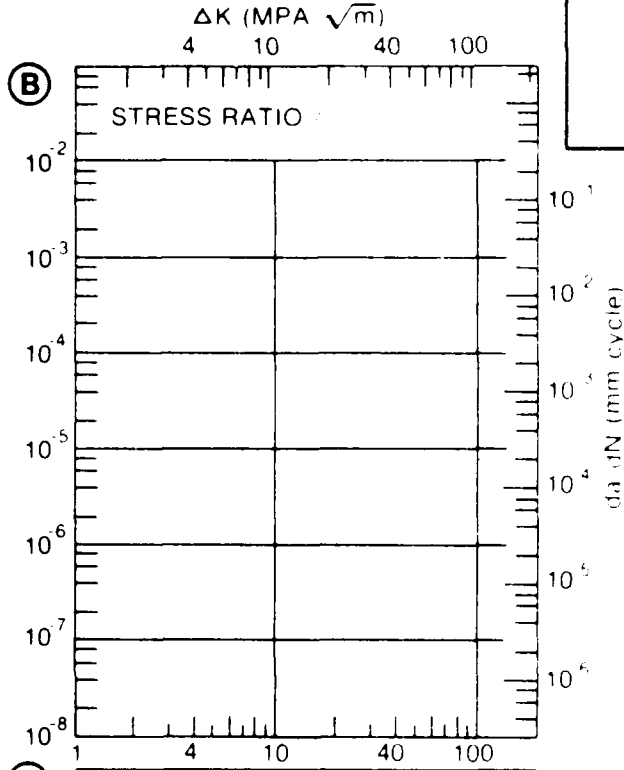
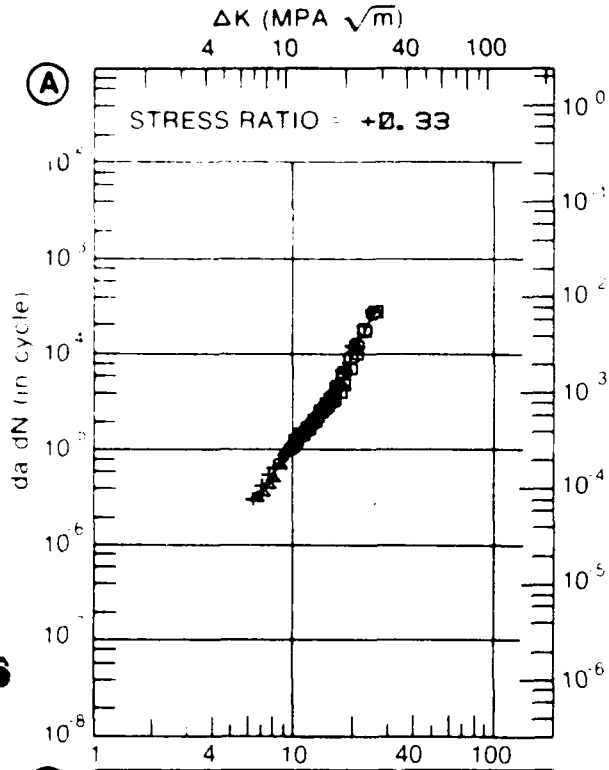


Figure 8.7.3.1

TABLE 8.7.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.2 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T6

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.			
DELTA K MIN	A: 6.00	4.98			
	B:				
	C:				
	D:				
	7.00	7.43			
	8.00	10.9			
	9.00	15.4			
10.00	21.3				
13.00	48.2				
16.00	89.5				
20.00	163.				
DELTA K MAX	A: 20.34	170.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 6.10
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T6
 FORM: 0.18" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 13.30 HZ

YIELD STRENGTH: 75.0 KSI
 ULT. STRENGTH: 83.2 KSI
 SPECIMEN THK: 0.176- 0.177"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: 86213

ALUM. ALLOY
7050

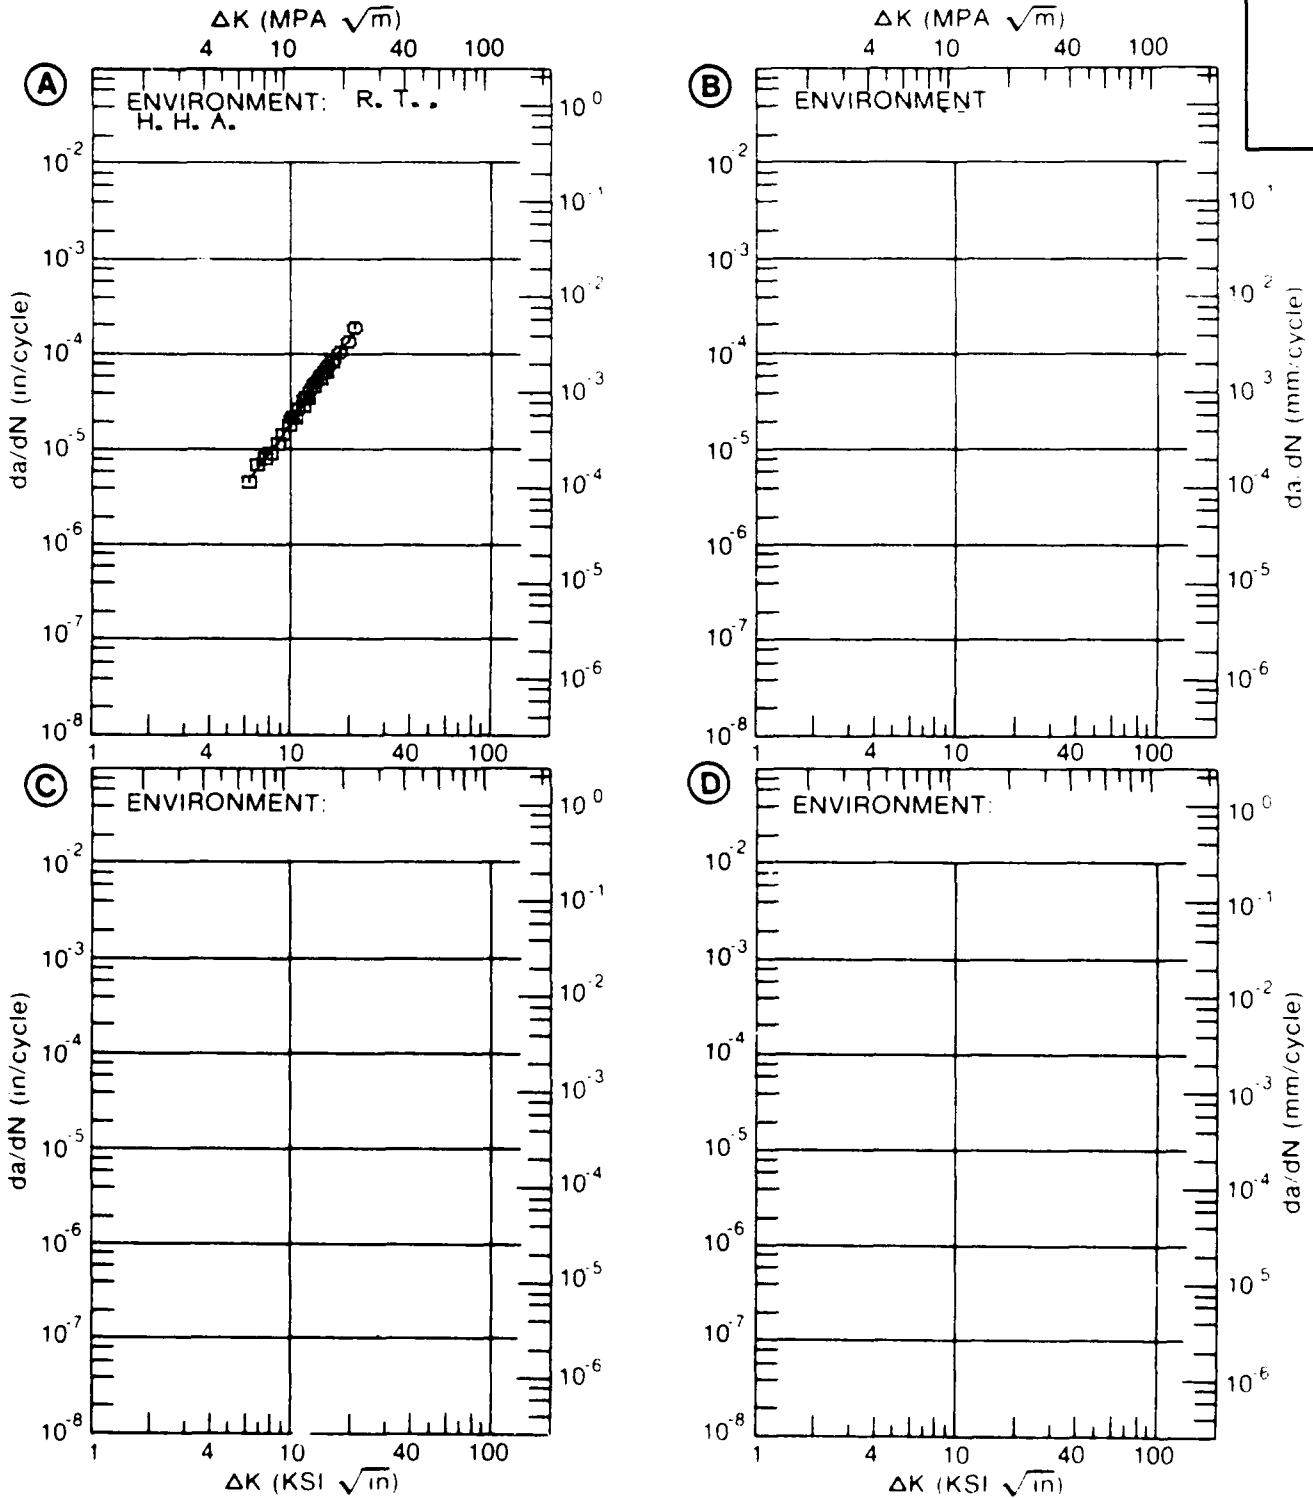


Figure 8.7.3.2

TABLE 8.7.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T6

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.			
DELTA K MIN	A:	6.88	6.37		
	B:				
	C:				
	D:				
		7.00	6.78		
		8.00	10.6		
		9.00	15.3		
		10.00	20.8		
DELTA K MAX		13.00	45.7		
		16.00	94.1		
		20.00	220.		
	A:	20.15	221.		
	B:				
	C:				
D:					

ROOT MEAN SQUARE 7.02
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2 0

CONDITION/HT: T6
 FORM: 0.18" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 13.30 HZ

YIELD STRENGTH: 74.5 KSI
 ULT STRENGTH: 82.7 KSI
 SPECIMEN THK: 0.180- 0.181"
 SPECIMEN WIDTH: 3.999- 4.000"
 REFERENCES: 86213

ALUM.
ALLOY

7050

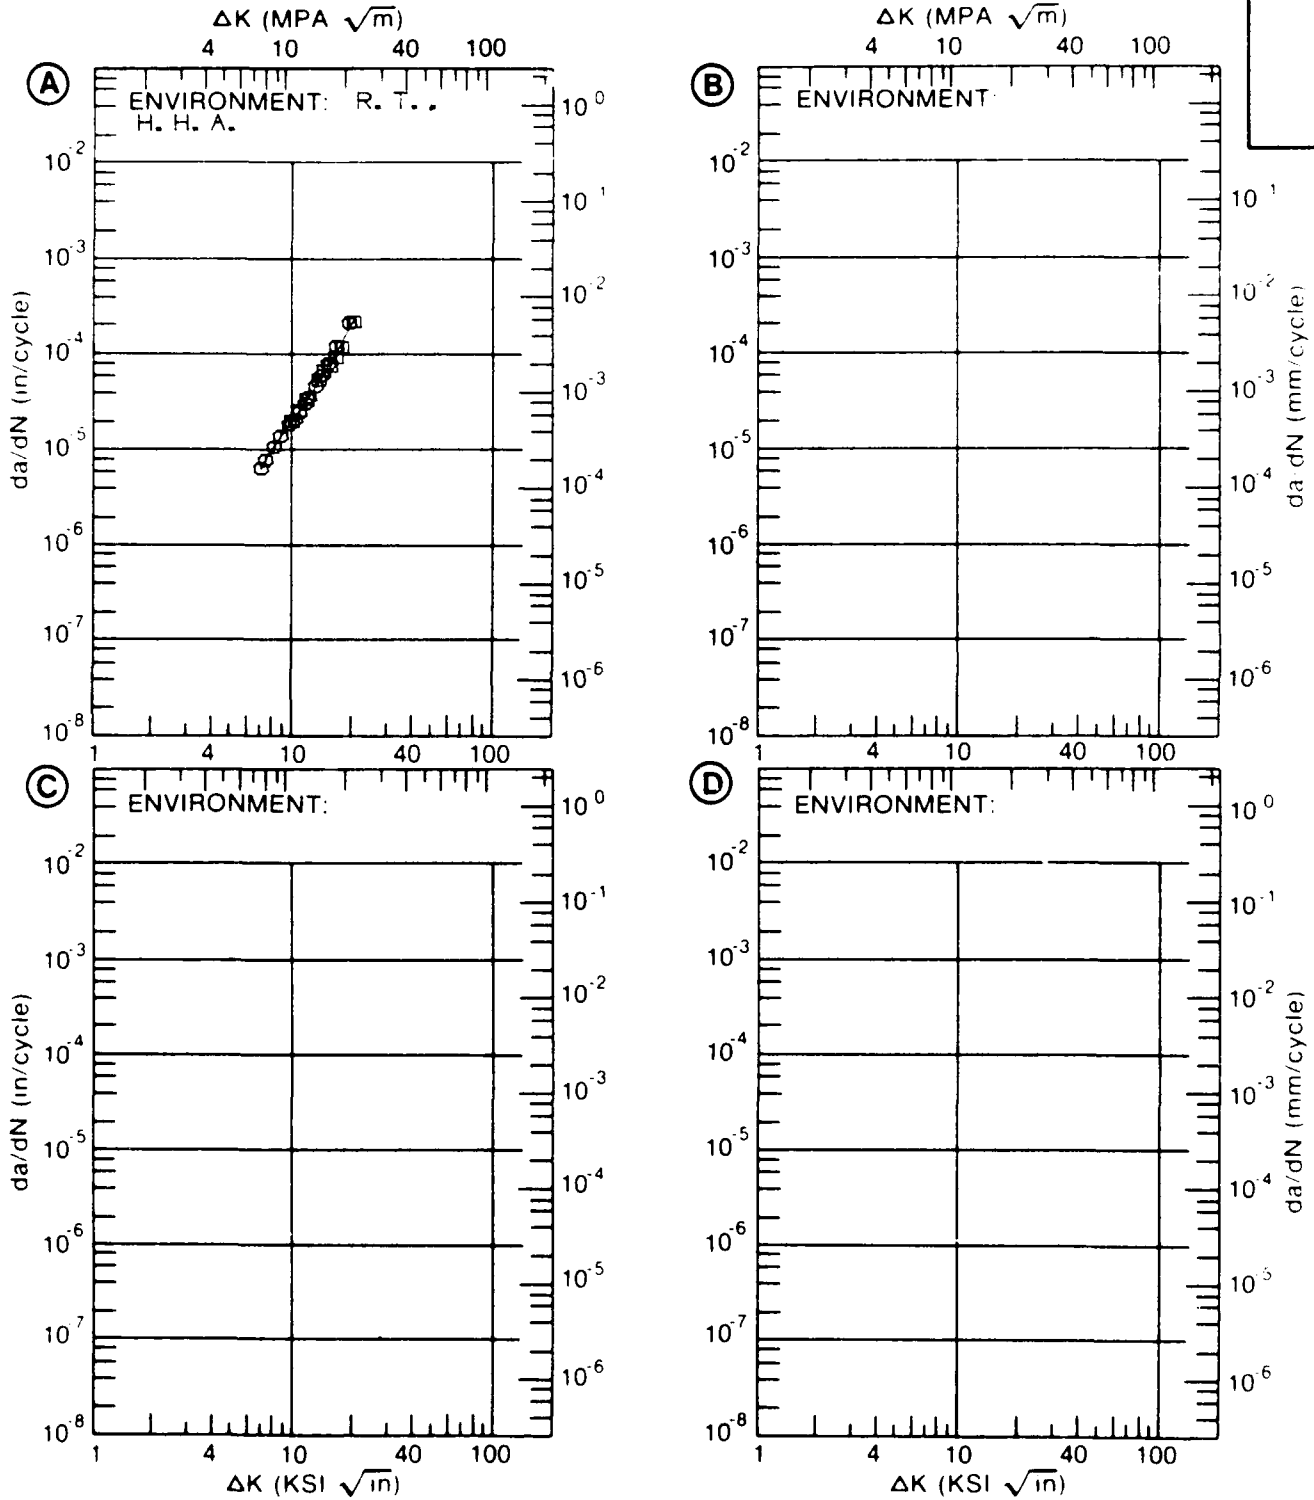


Figure 8.7.3.3

TABLE 8.7.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.4 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		7050			
CONDITION: T73					
ENVIRONMENT: R T J L H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.08			
DELTA K B:	A: 12.21	.227			
MIN C:					
D:					
	13.00	.427			
	16.00	1.27			
	20.00	12.6			
	25.00	29.2			
DELTA K B:	A: 28.21	64.2			
MAX C:					
D:					
ROOT MEAN SQUARE		9.95			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1			
SUMMARY	1.25-2.0				
(NP/NA)	2.0				

CONDITION/HT: T73
 FORM: FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 71.0 KSI
 ULT STRENGTH: 78.0 KSI
 SPECIMEN THK: 0.500"
 SPECIMEN WIDTH: 2.810"
 REFERENCES: 88579

ALUM. ALLOY
7050

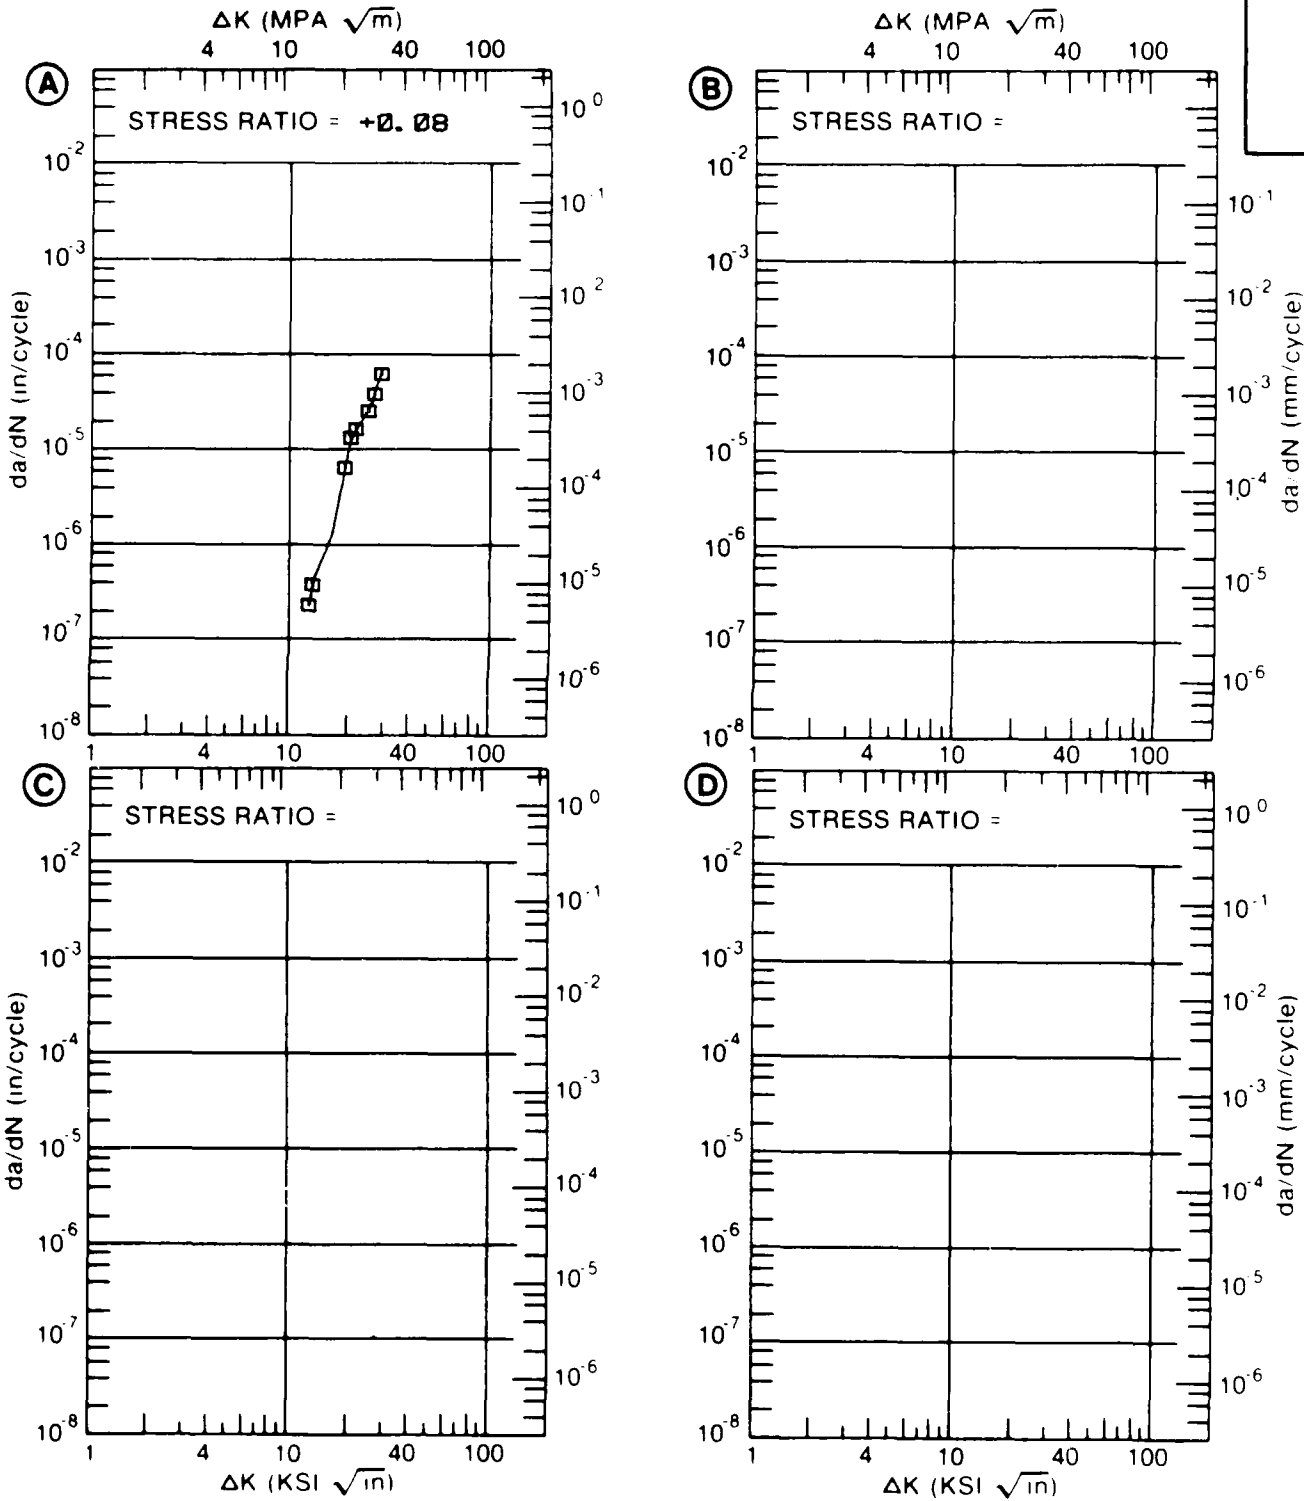


Figure 8.7.3.4

TABLE 8.7.3.5

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.5 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7351

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	E= R. I. 3.5% NaCl			
DELTA K MIN	A: 3.01	B: 8	C: .017	D:
	3.50		.102	
	4.00		.271	
	5.00		.765	
	6.00		1.67	
	7.00		3.27	
	8.00		5.76	
	9.00		9.22	
	10.00		13.5	
	13.00		29.9	
	16.00		49.3	
	20.00		78.5	
	25.00		121.	
DELTA K MAX	A: 27.97	B:	C: 152.	D:

ROOT MEAN SQUARE 10.75
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) 2.0

CONDITION/HT: T7351
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT STRENGTH:
 SPECIMEN THK: 0.151"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 86844

ALUM. ALLOY
7050

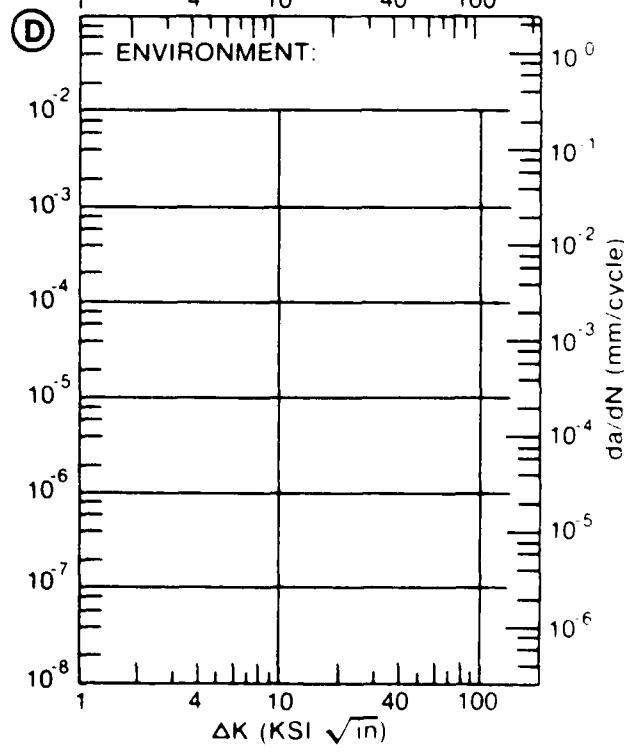
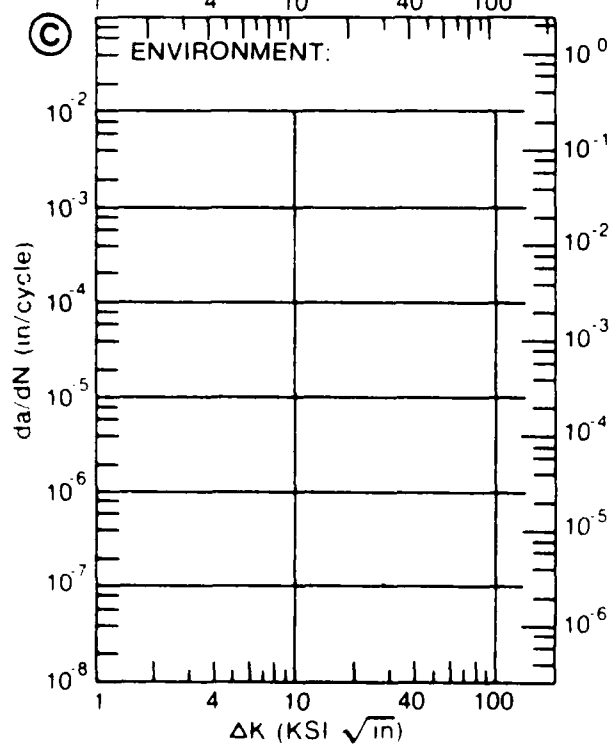
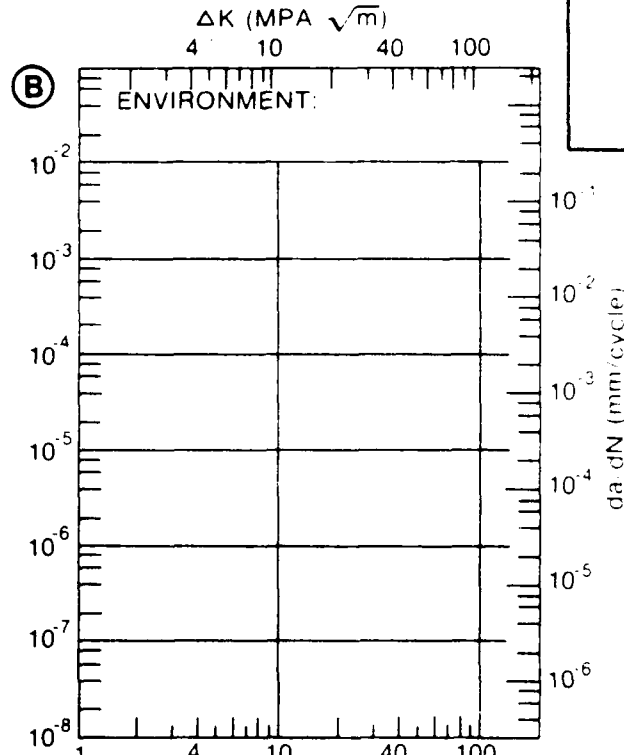
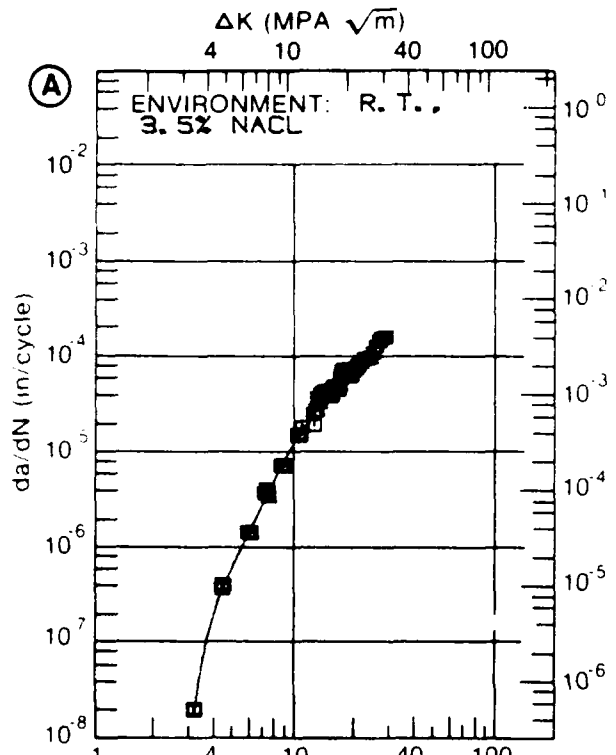


Figure 8.7.3.5

TABLE 8.7.3.6

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.6 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7351

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.	E= R. T. 3. 5% NA CL		
DELTA K	A: 6. 08	1. 52			
MIN	B: 5. 19		. 272		
	C:				
	D:				
	6. 00		1. 15		
	7. 00	2. 47	4. 36		
	8. 00	3. 71	9. 90		
	9. 00	5. 15	16. 2		
	10. 00	6. 79	22. 9		
	13. 00	13. 1	54. 4		
	16. 00	22. 3	106.		
	20. 00	42. 1	171.		
	25. 00	83. 3	237.		
	30. 00	141.	318.		
DELTA K	A: 30. 08	142.			
MAX	B: 32. 15		367.		
	C:				
	D:				

ROOT MEAN SQUARE 6. 27 8. 42
PERCENT ERROR

LIFE 0. 0-0. 5
PREDICTION 0. 5-0. 8
RATIO 0. 8-1. 25 1
SUMMARY 1. 25-2. 0 1
(NP/NA) >2. 0

CONDITION: HT. T7351
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 2.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.148- 0.152"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 86844

ALUM. ALLOY
7050

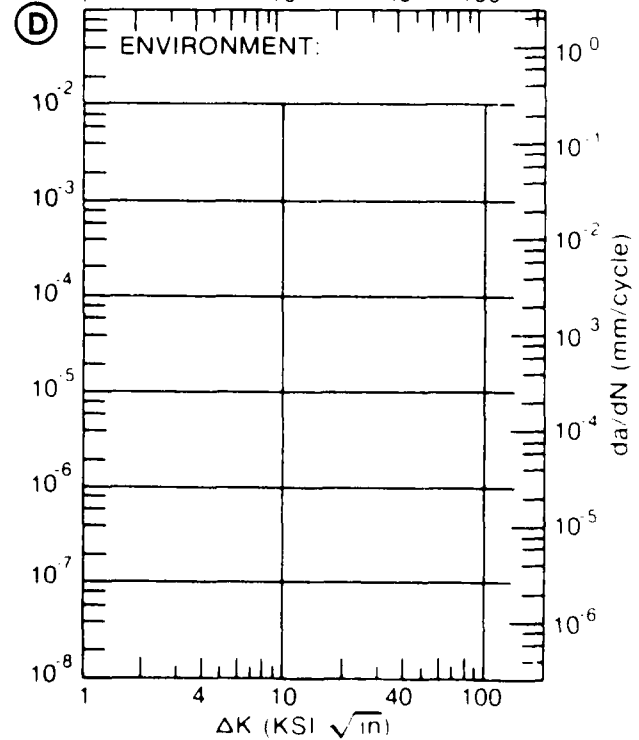
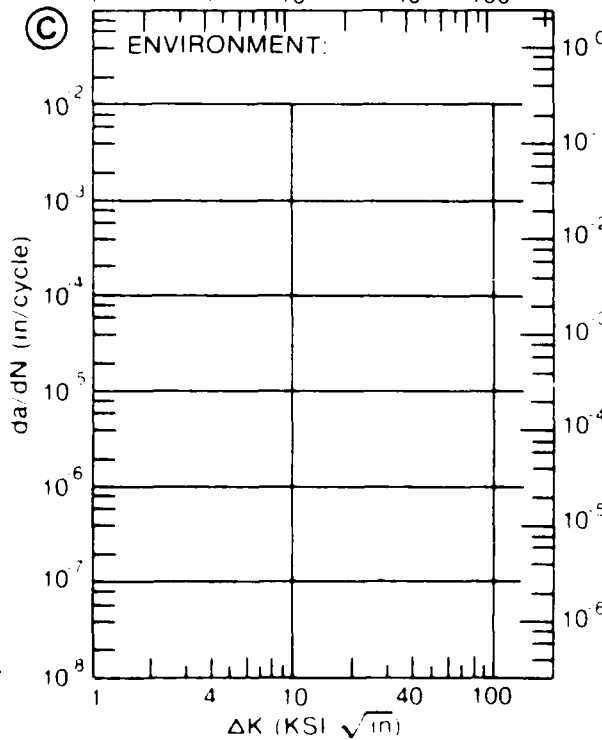
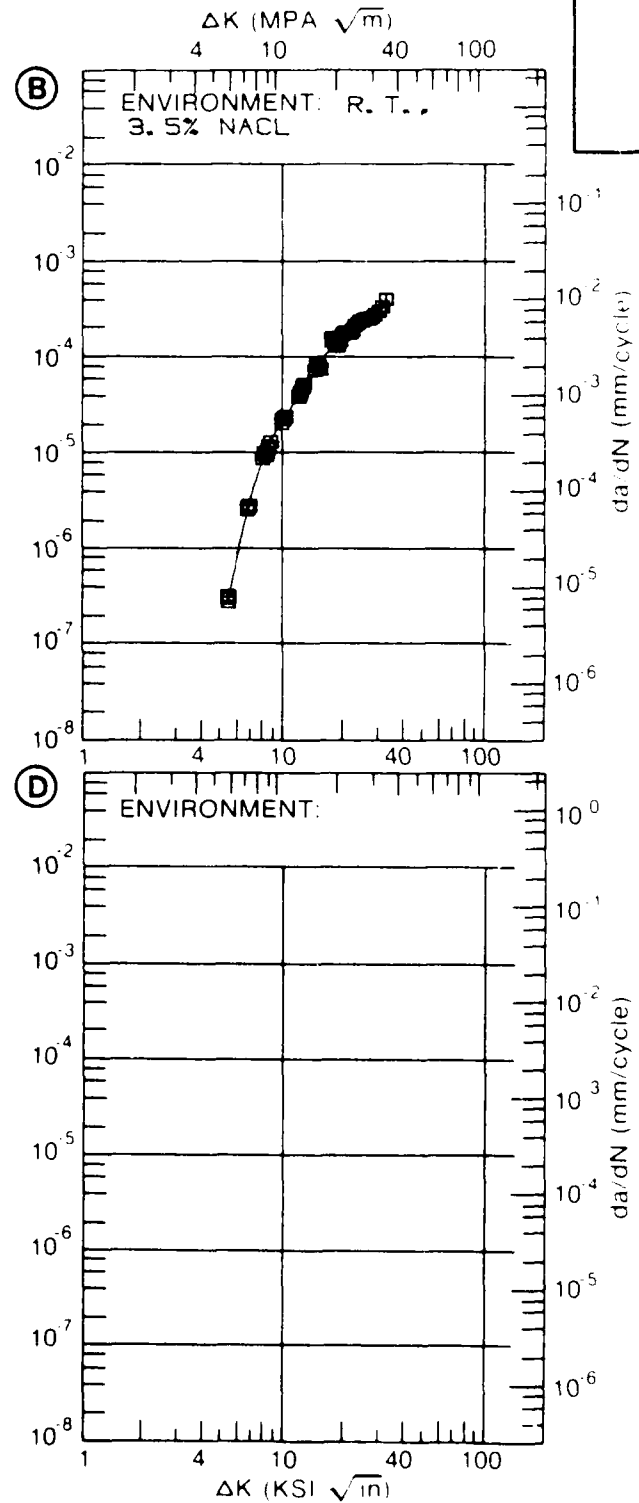
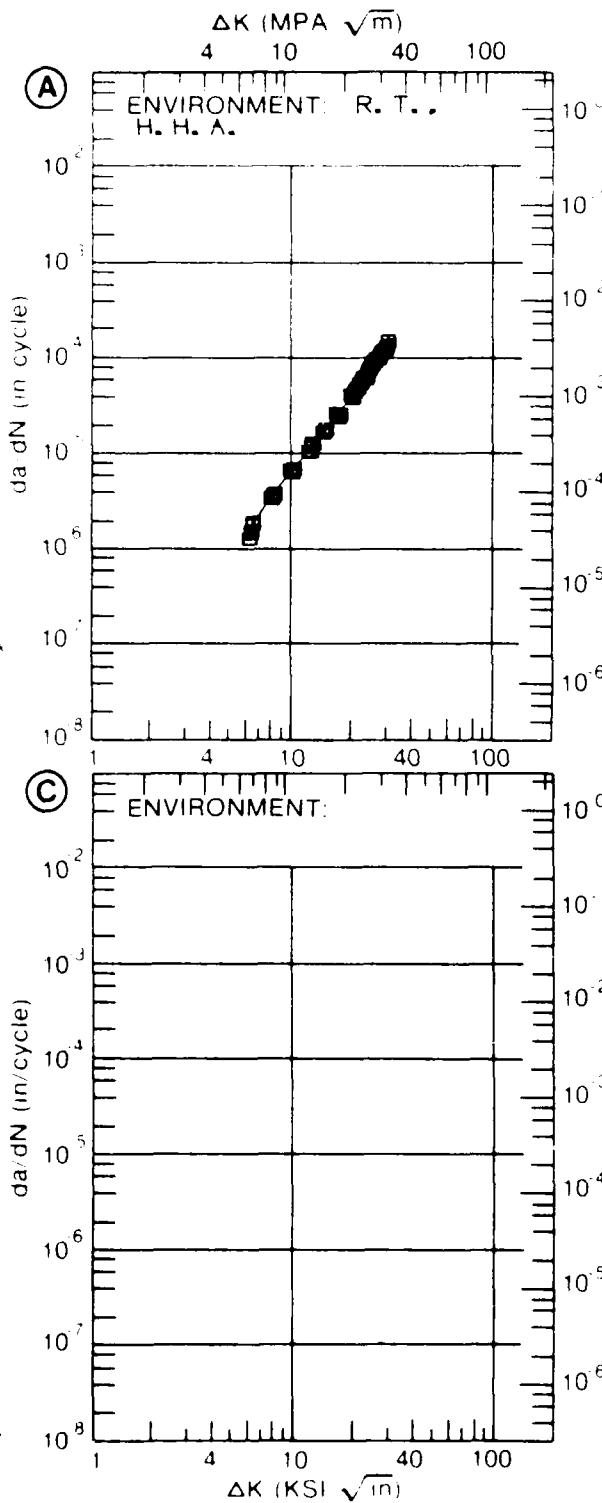


Figure 8.7.3.6

TABLE 8.7.3.7

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.7 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL ALUMINUM 7050 CONDITION T7351					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R I DRY AIR	E= R T S T W		
DELTA K MIN	A: 5.69	822	1.94		
	B: 5.16				
	C:				
	D:				
	6.00	942	4.30		
	7.00	1.64	8.88		
	8.00	3.01	13.2		
	9.00	4.93	16.6		
	10.00	6.92	20.4		
	13.00	13.0	42.8		
	16.00	22.8			
	20.00	62.1			
DELTA K MAX	A: 20.51	72.4	45.1		
	B: 15.33				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		10.72	14.34		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0				

CONDITION/HT T7351
 FORM 2.00- 4.00 TH PLATE
 SPECIMEN TYPE CT
 ORIENTATION LT
 STRESS RATIO +0.33
 FREQUENCY 2.00- 20.00 Hz

YIELD STRENGTH 1000 MPa
 UTS STRENGTH 1200 MPa
 SPECIMEN THK 2.00
 SPECIMEN WIDTH 10.00
 REFERENCES 1,2,3

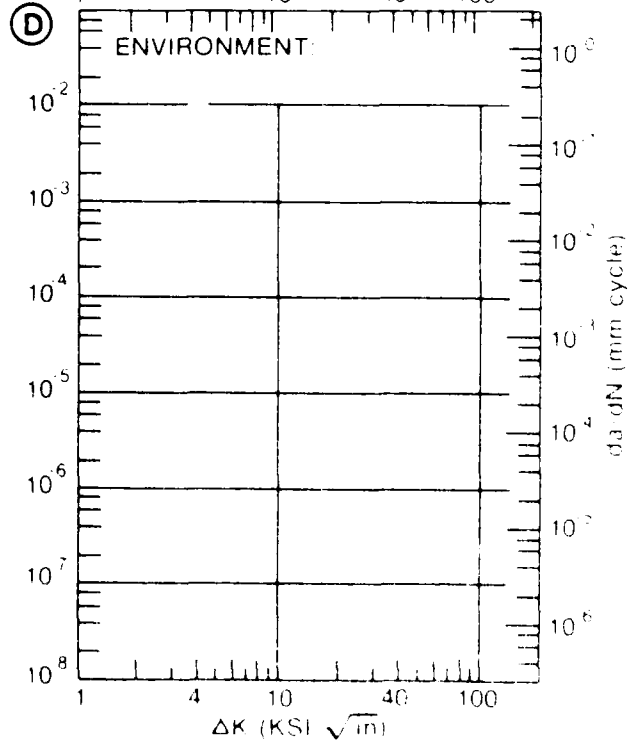
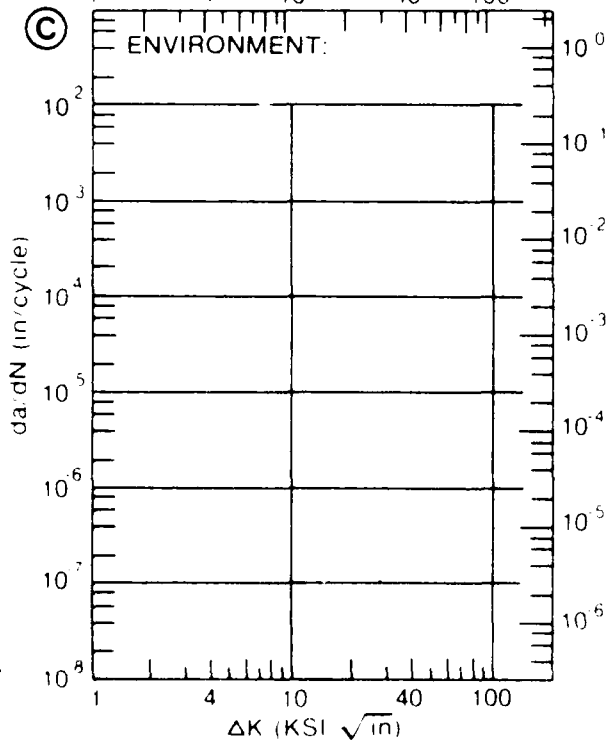
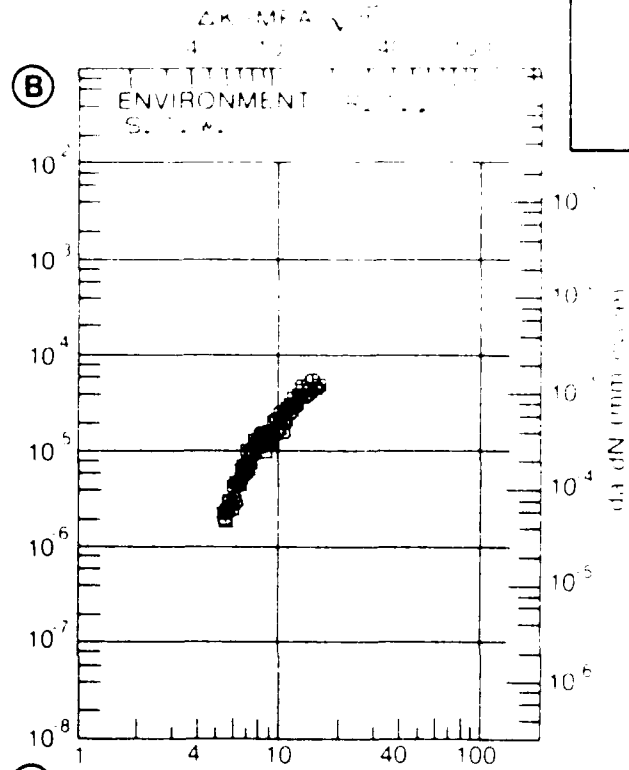
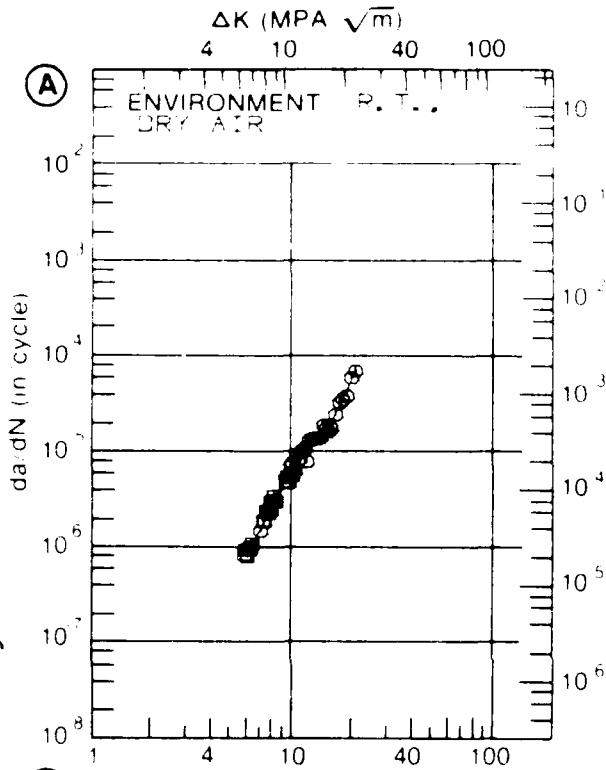
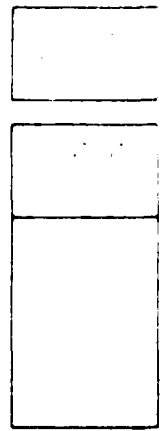


Figure 8.7.3.7

TABLE 8.7.3.8

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.8 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7351

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. S. T. W.	
DELTA K MIN	A: 5.89 : B: 5.68 : C: 4.52 : D:	856	1.36	1.58
	5.00 : 6.00 : 7.00 : 8.00 : 9.00 : 10.00 : 13.00 : 16.00 :	.981 1.86 3.63 6.11 8.65 19.1 49.0	1.87 4.08 6.44 8.73 11.2 25.8 62.3	1.72 3.69 7.26 12.0 16.7 21.0 35.9 56.2
DELTA K MAX	A: 18.96 : B: 18.14 : C: 17.01 : D:	89.2	134.	61.7
ROOT MEAN SQUARE PERCENT ERROR	24.19	13.88	18.31	

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T7351
 FORM: 2.00- 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 1.50- 20.00 HZ

YIELD STRENGTH: 60.9- 63.4 KSI
 ULT. STRENGTH: 72.1- 74.4 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL001

ALUM.
 ALLOY
 7252

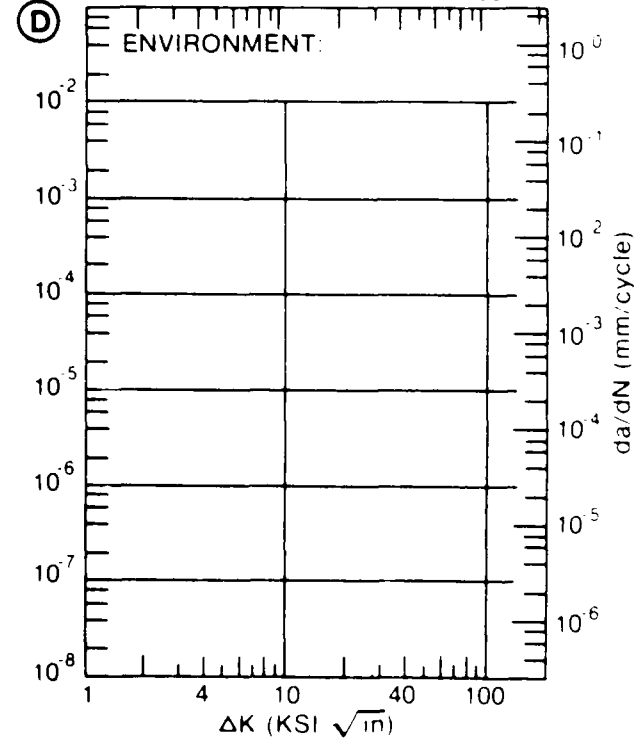
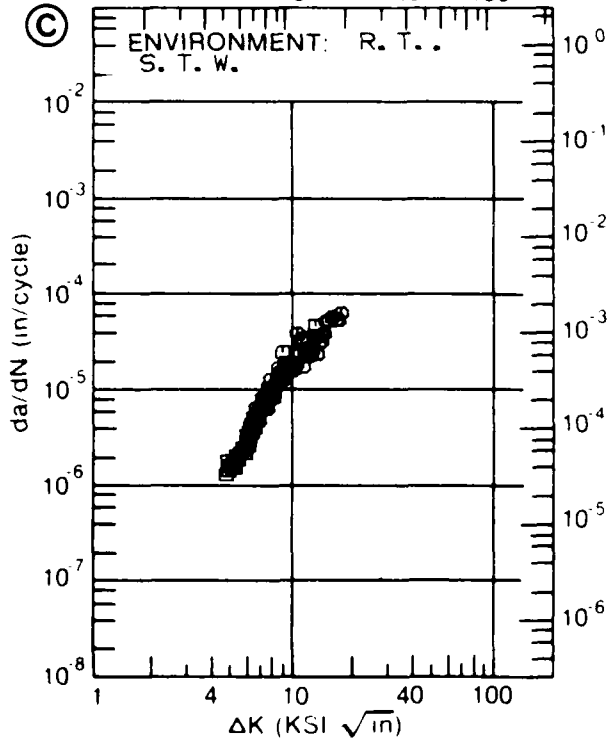
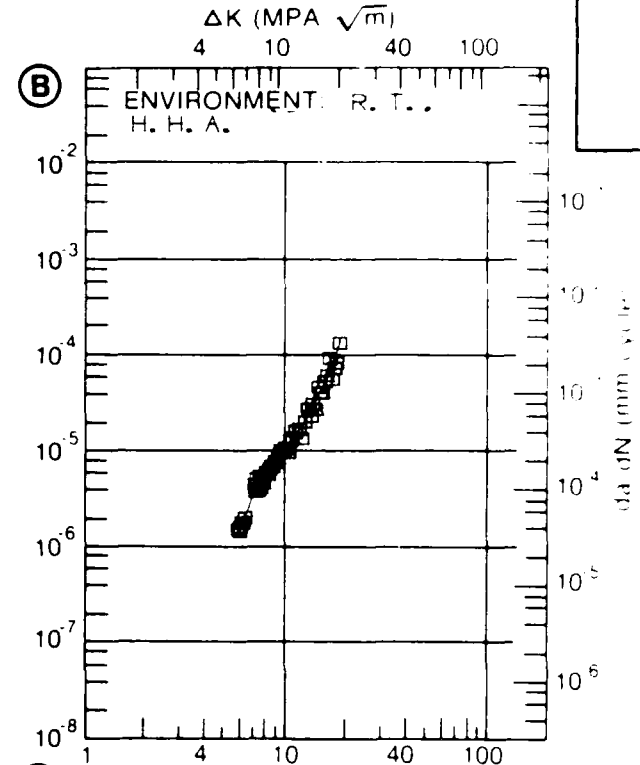
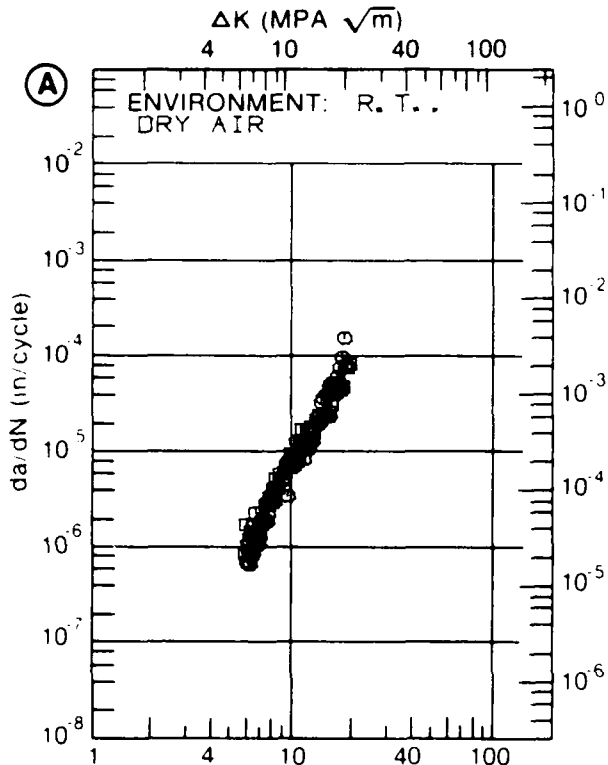


Figure 8.7.3.8

TABLE 8.7.3.9

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.9 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T7351					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. S. T. W.		
DELTA K MIN	A:	5.28	.839		
	B:				
	C:	6.00	.937		
	D:	7.00	1.77		
DELTA K MAX	A:	7.69	2.77		
	B:				
	C:				
	D:				
ROOT MEAN SQUARE PERCENT ERROR		10.40	0.00		
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY (NP/NA)	1.25-2.0 >2.0				

CONDITION/HT: T7351
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.67
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 63.4 KSI
 ULT. STRENGTH: 74.4 KSI
 SPECIMEN THK: 0.250"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: AL001

ALUM.
ALLOY

7050

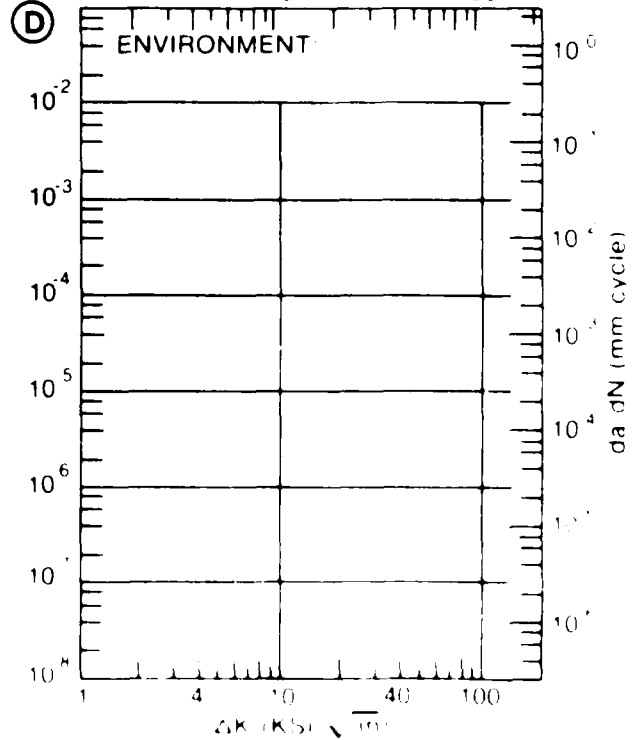
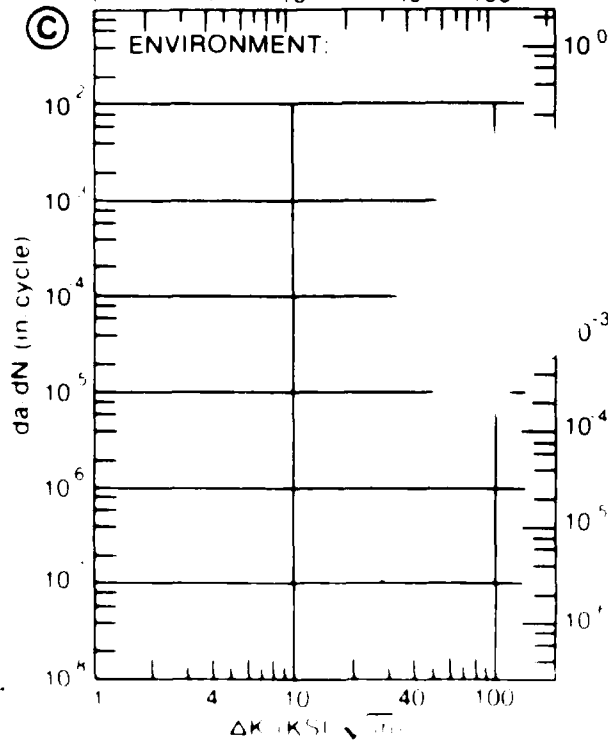
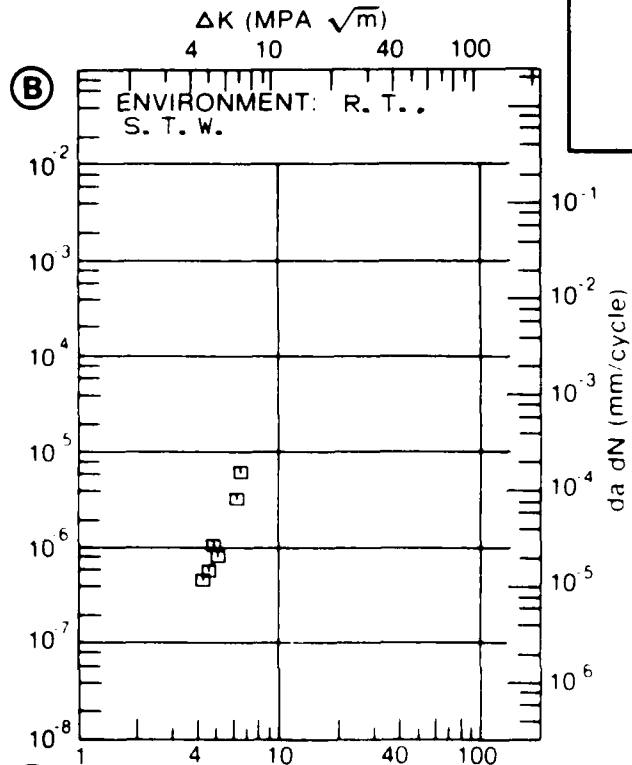
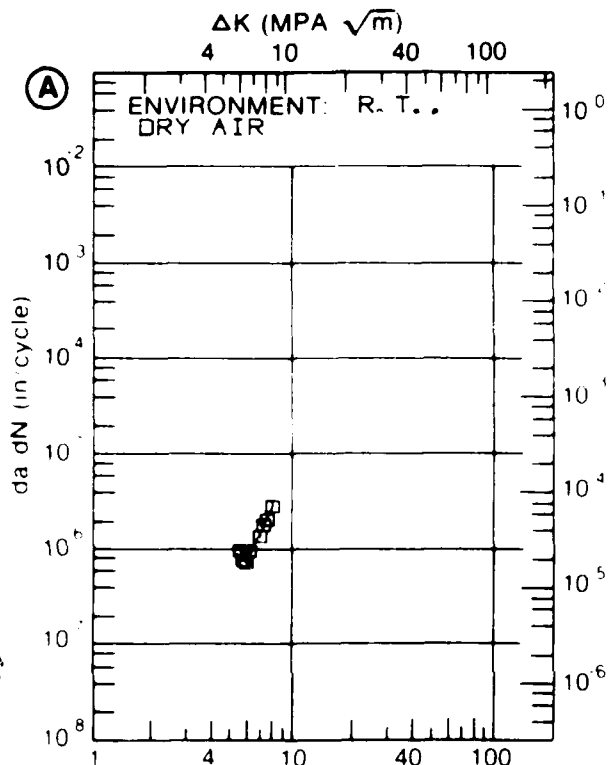


TABLE 8.7.3.10

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.10 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7351

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. DRY AIR 1.5-15HZ	E= R. T. H. H. A. 10-20HZ	E= R. T. S. T. W., 20HZ	
DELTA K MIN	A: 5.73 : .995	B: 5.73 : 1.78	C: 5.72 : 4.28	D:
	6.00 : 1.01	7.00 : 1.73	8.00 : 4.82	
	8.00 : 2.09	9.00 : 3.33	10.00 : 7.80	
	9.00 : 3.65	11.00 : 6.00	13.00 : 11.8	
	10.00 : 5.36	13.00 : 8.85	16.00 : 15.8	
	13.00 : 7.36	19.7 : 26.8		
	16.00 : 19.7	73.2 : 78.4		
DELTA K MAX	A: 18.78 : 193.	B: 17.68 : 192.	C: 11.73 : 27.5	D:
ROOT MEAN SQUARE	16.80	15.19	13.74	
PERCENT ERROR				

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T7351
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: 0.33
 FREQUENCY:

YIELD STRENGTH: 60.0 KSI
 ULT. STRENGTH: 72.4 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.605"
 REFERENCES: AL001

ALUM.
 ALLOY

7050

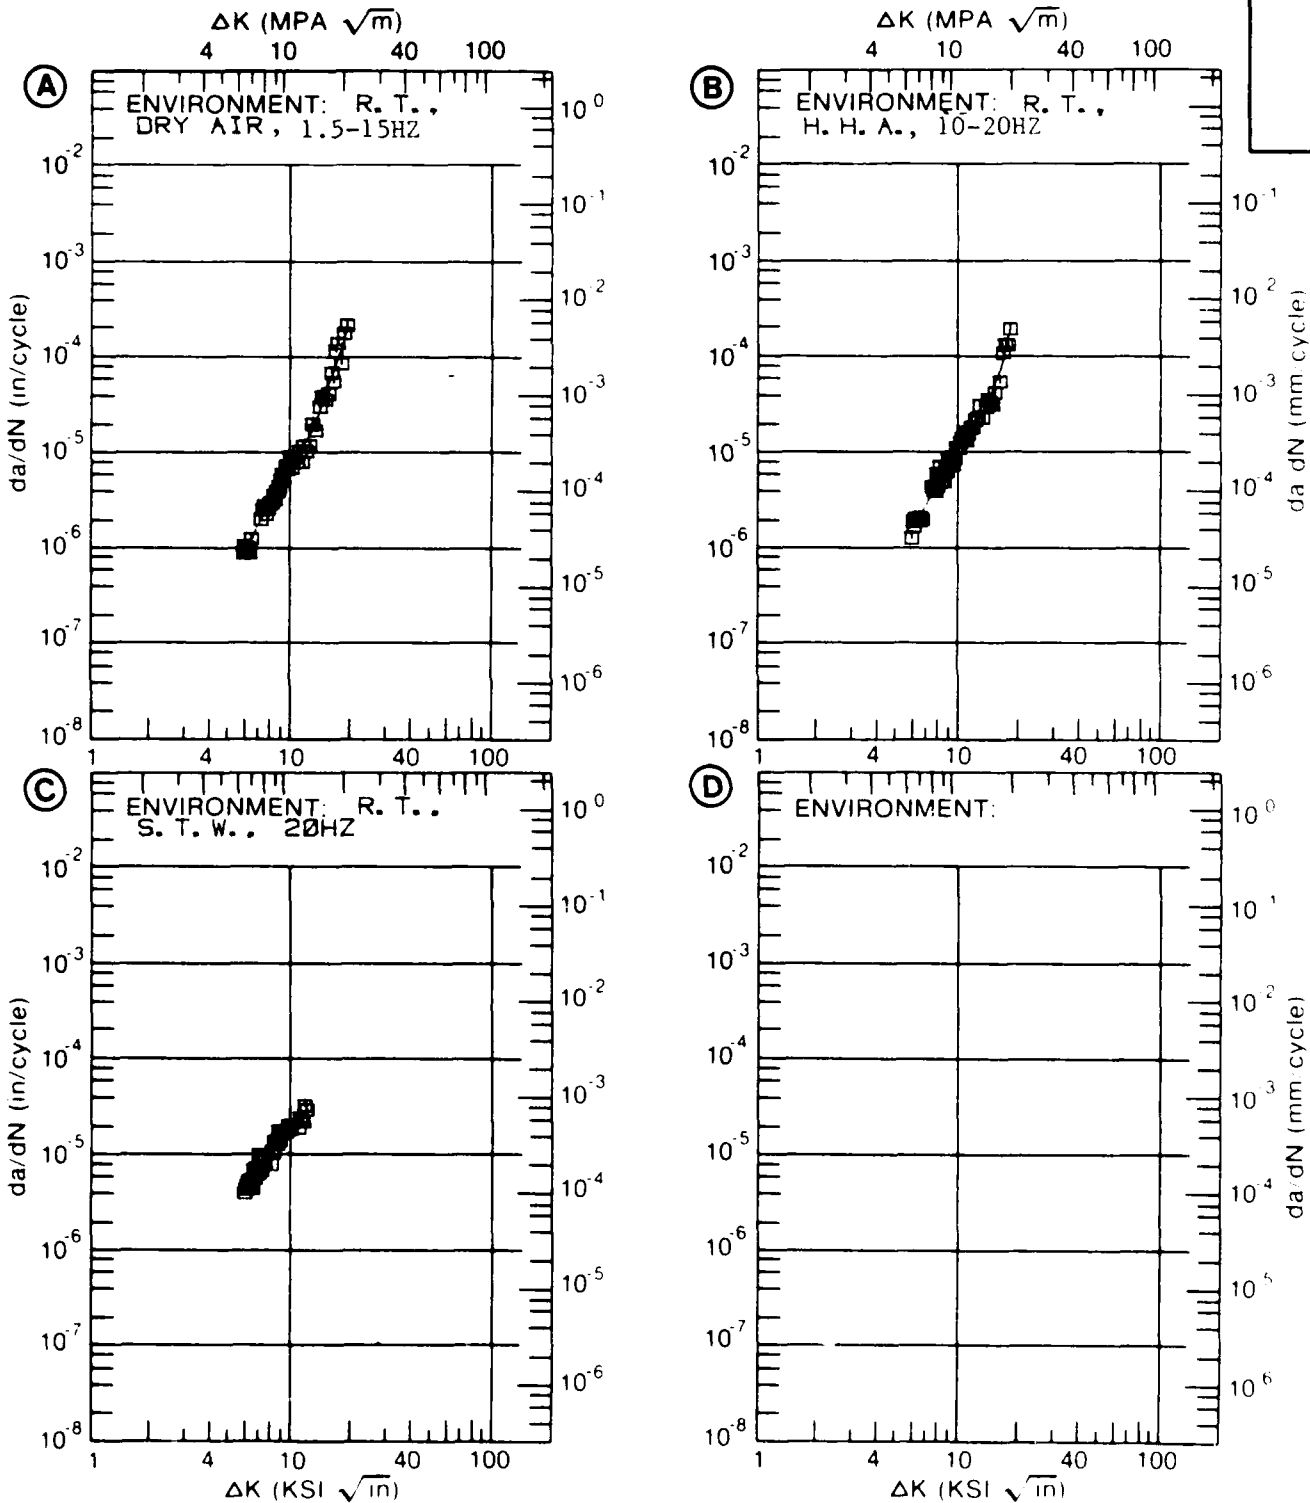


Figure 8.7.3.10

TABLE 8.7.3.11

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.11 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T7351X					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.		
DELTA K MIN	A: 4.55	.397			
	B: 3.54		.262		
	C:				
	D:				
	4.00		.457		
	5.00	.495	1.21		
	6.00	.680	2.58		
	7.00	.974	4.70		
	8.00	1.50	7.65		
	9.00	2.32	11.4		
	10.00	3.48	15.9		
	13.00	9.55	32.7		
	16.00	20.1	50.6		
DELTA K MAX	A: 18.90	33.6			
	B: 17.49		58.7		
	C:				
	D:				
ROOT MEAN SQUARE		7.12	9.78		
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	2		

CONDITION/HT: T7351X
 FORM: 0.91" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.899- 0.900"
 SPECIMEN WIDTH: 3.100"
 REFERENCES: AL007

ALUM. ALLOY
7050

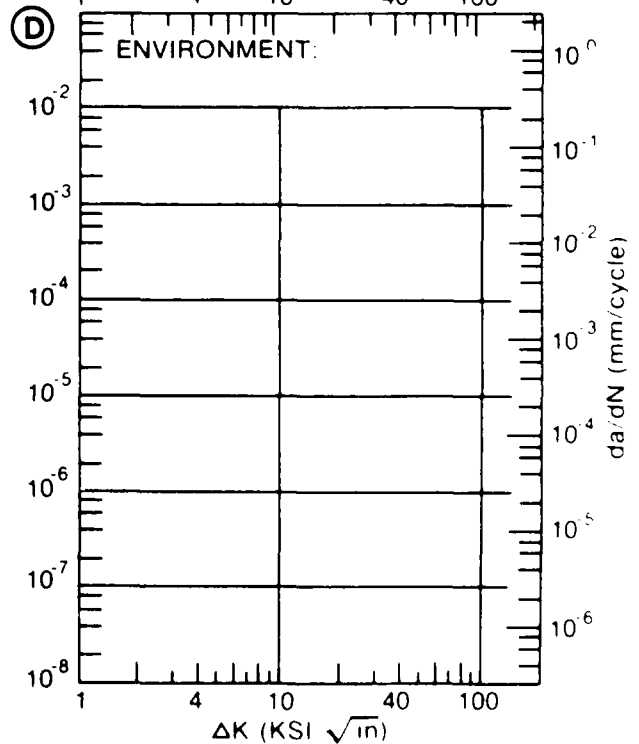
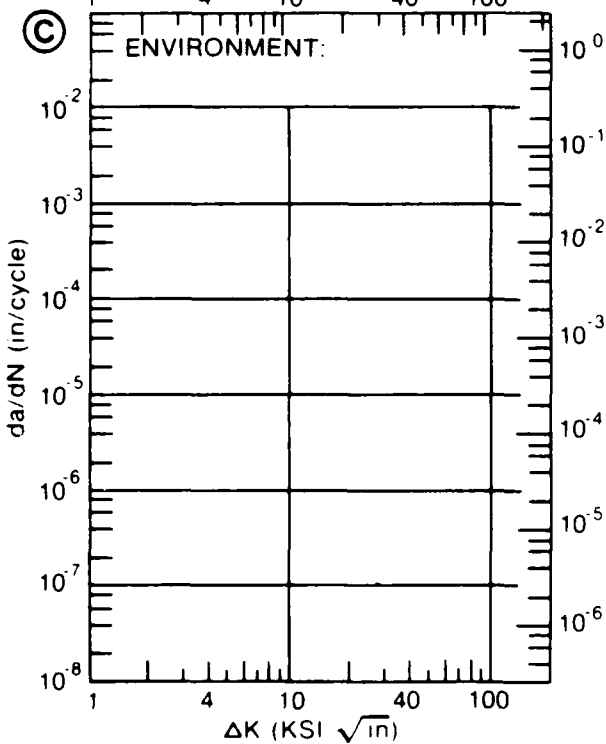
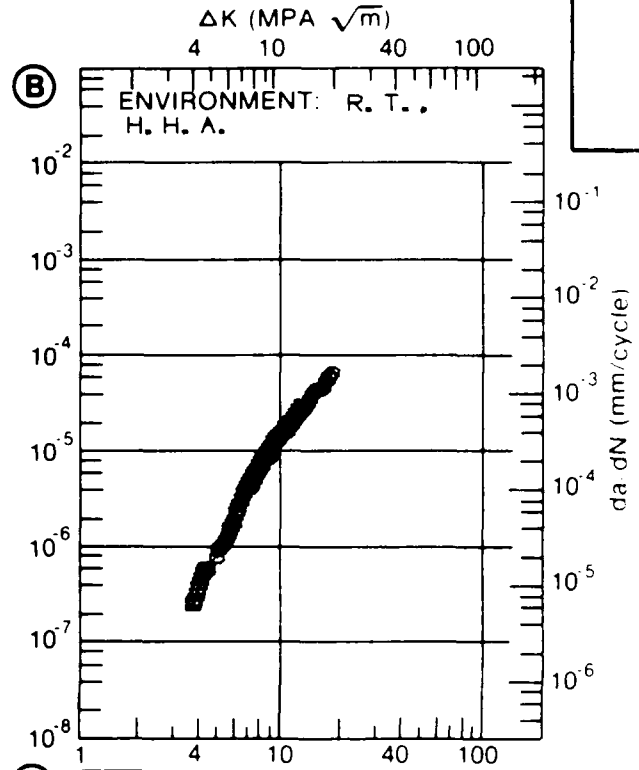
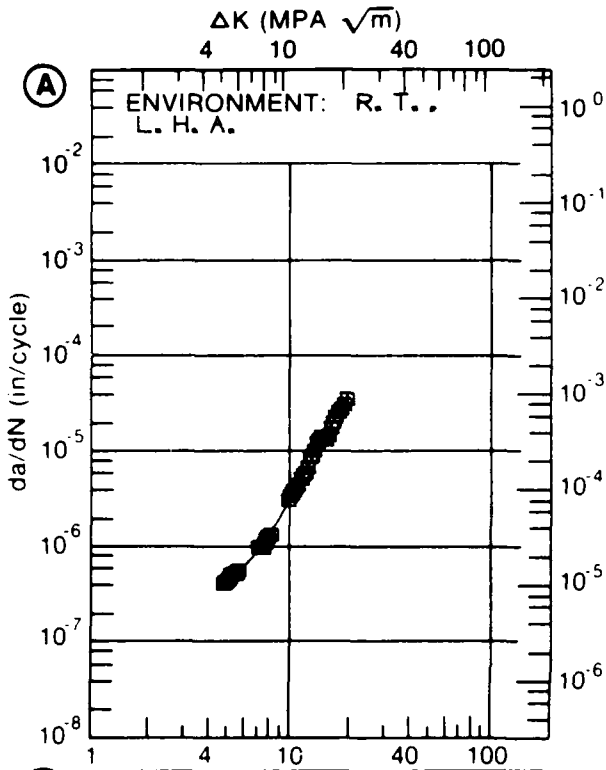


Figure 8.7.3.11

TABLE 8.7.3.12

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.12 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T7351X					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.		
DELTA K	A: 3.70	.201			
MIN	B: 3.72		.376		
	C:				
	D:				
	4.00	.335	.454		
	5.00	1.06	2.25		
	6.00	2.08	4.21		
	7.00	3.25	6.74		
	8.00	4.53	9.95		
	9.00	5.97	13.9		
	10.00	7.69	18.4		
	13.00	16.3	35.7		
	16.00	37.7			
DELTA K	A: 16.93	50.0			
MAX	B: 14.95		49.4		
	C:				
	D:				
ROOT MEAN SQUARE		22.77	7.56		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	2		
SUMMARY	1.25-2.0	1			
(NP/NA)	2.0				

CONDITION/HT: T7351X
 FORM: 0.91" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.899- 0.900"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL007

ALUM. ALLOY
7050

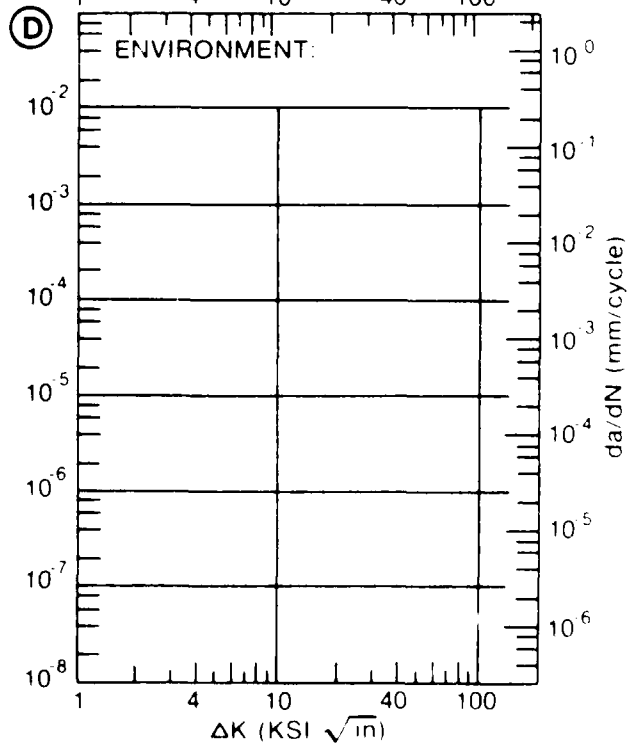
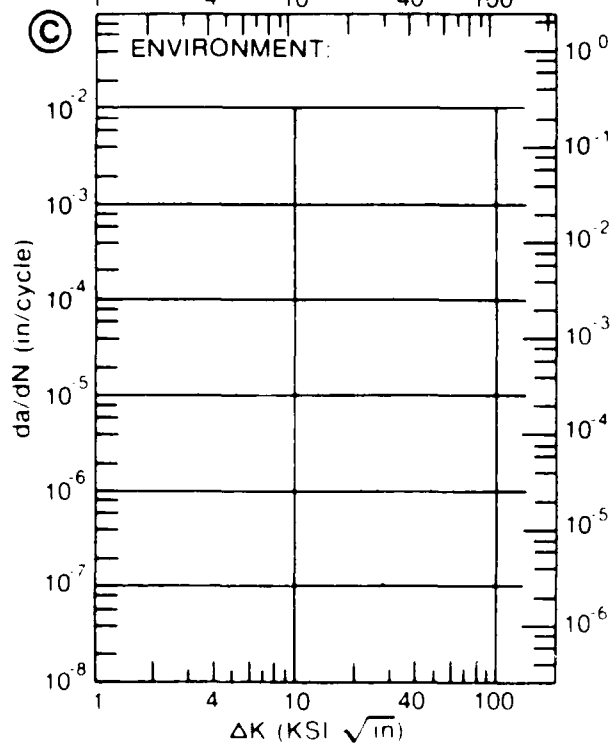
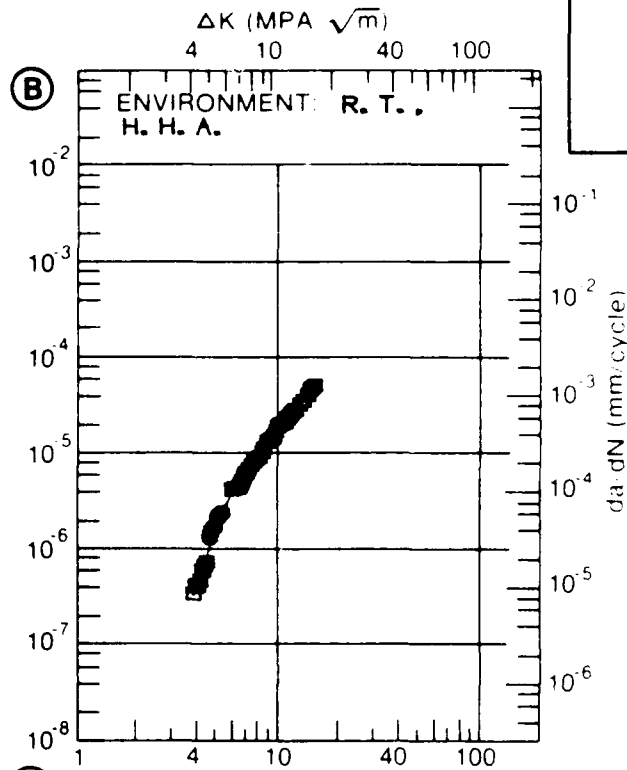
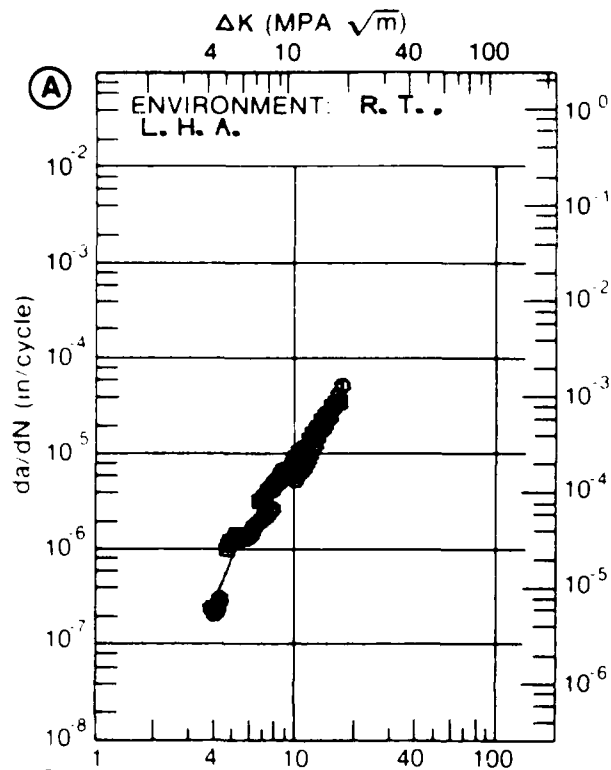


Figure 8.7.3.12

TABLE 8.7.3.13

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.13 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T7351X					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.		
DELTA K	A: 3.95	.352			
MIN	B: 2.90		.174		
	C:				
	D:				
	3.00		.170		
	3.50		.295		
	4.00	.372	.573		
	5.00	.862	1.41		
	6.00	1.69	2.62		
	7.00	2.97	4.33		
	8.00	4.69	6.83		
	9.00	6.78	10.7		
	10.00	9.90	16.6		
	13.00	64.8	68.2		
DELTA K	A: 13.94	157.			
MAX	B: 14.35		134.		
	C:				
	D:				
ROOT MEAN SQUARE		19.29	12.88		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	2		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T7351X
 FORM: 5.00" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.990- 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL007

ALUM. ALLOY
7050

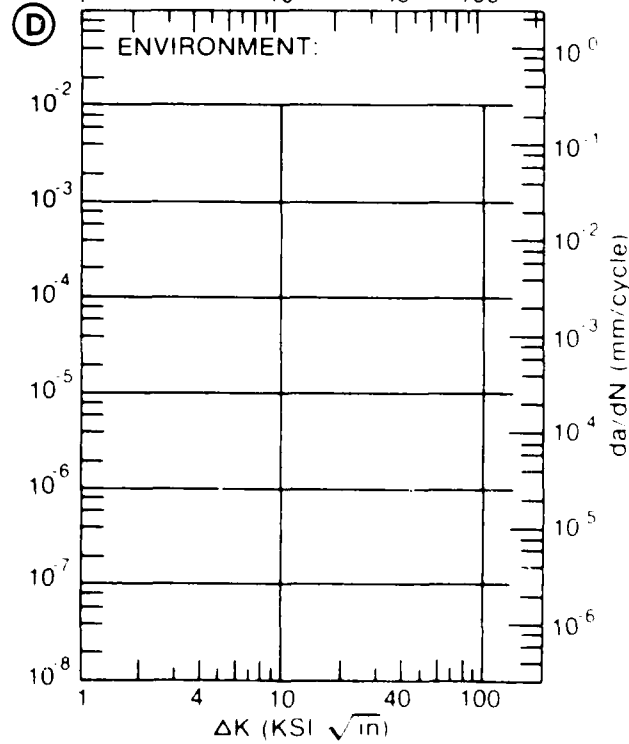
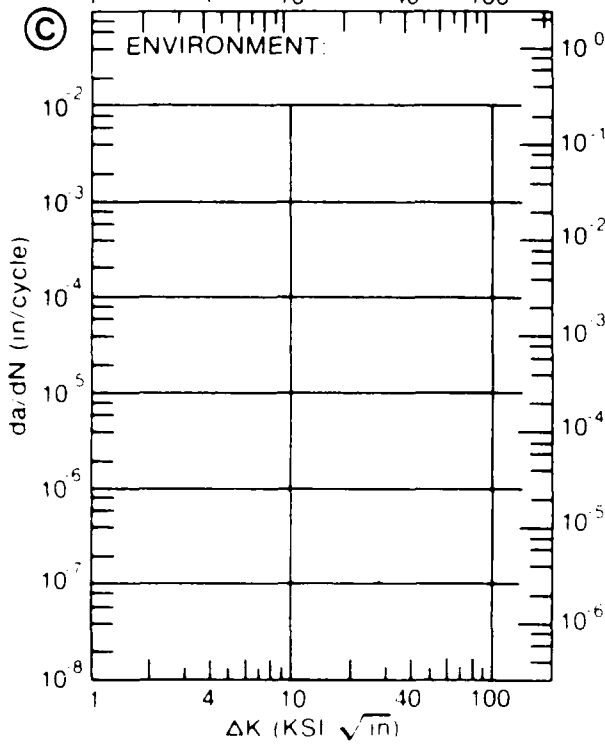
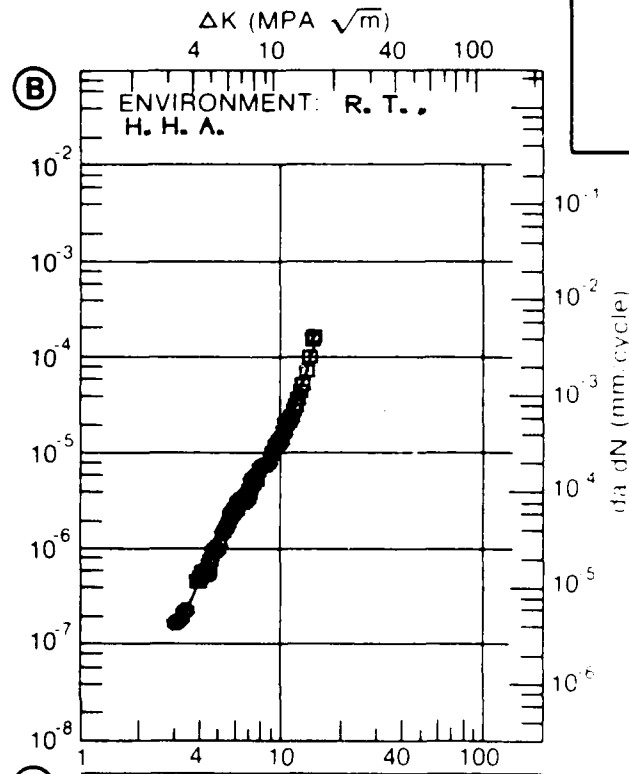
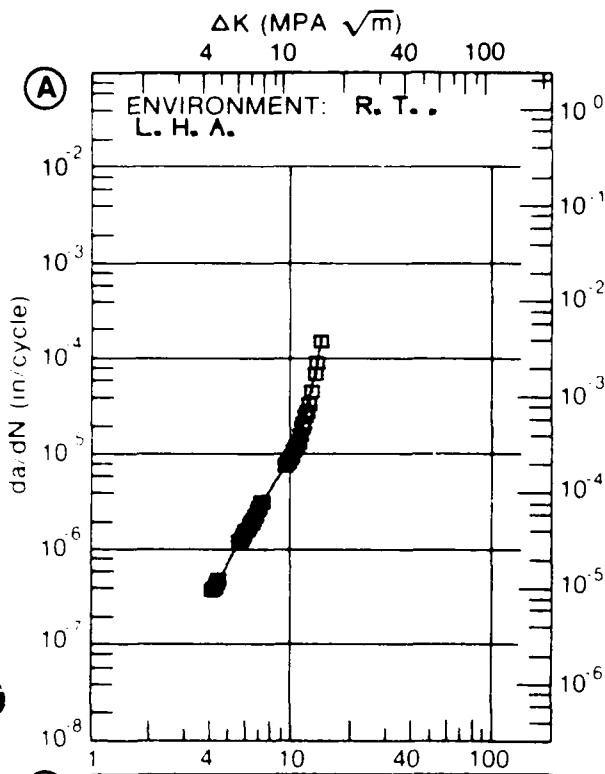


Figure 8.7.3.13

TABLE 8.7.3.14

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.14 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7351X

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.	E= R. T. H. H. A.		
DELTA K MIN	A: 3.73	486		
	B: 3.76		756	
	C:			
	D:			
	4.00	568	880	
	5.00	810	1.38	
	6.00	1.08	2.47	
	7.00	1.45	4.45	
	8.00	1.96	7.05	
	9.00	2.67	9.43	
	10.00	3.67	11.2	
	13.00	9.91	19.4	
	16.00	55.1	61.0	
DELTA K MAX	A: 16.18	70.0		
	B: 16.55		81.4	
	C:			
	D:			

ROOT MEAN SQUARE 16.45 10.26
PERCENT ERROR

LIFE 0.0-0.9
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T7351X
 FORM: 5.00" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: S-T
 STRESS RATIO: +0.33
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.998- 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL007

ALUM.
ALLOY

7050

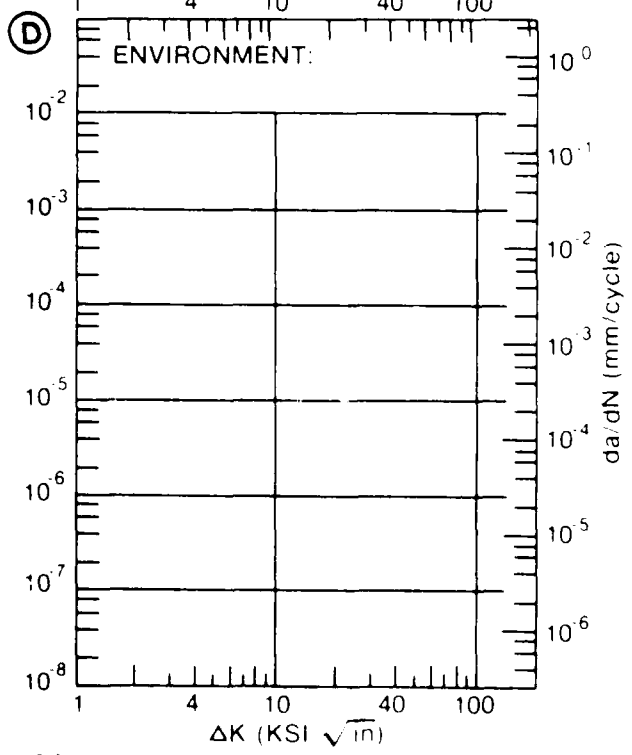
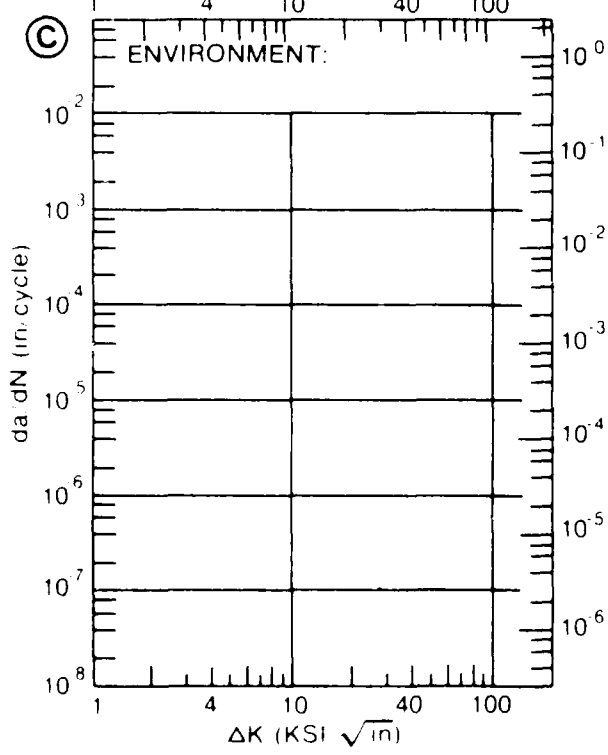
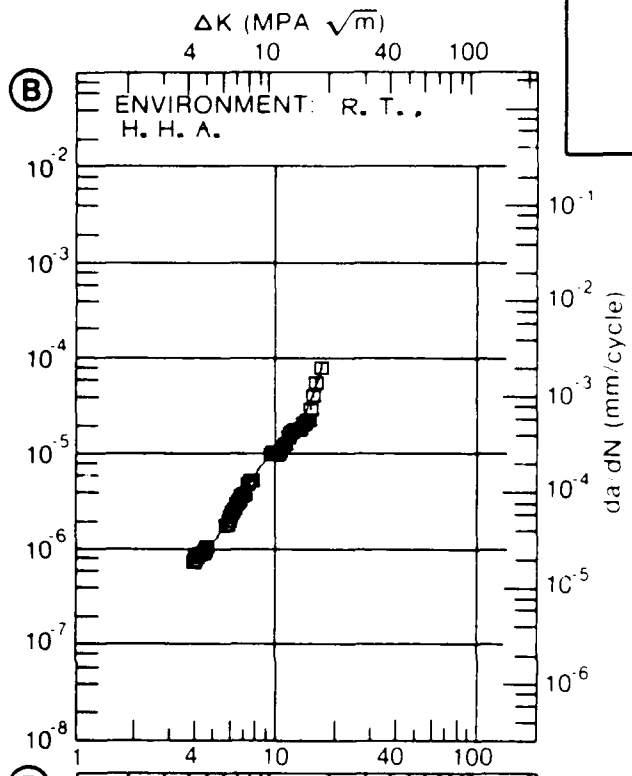
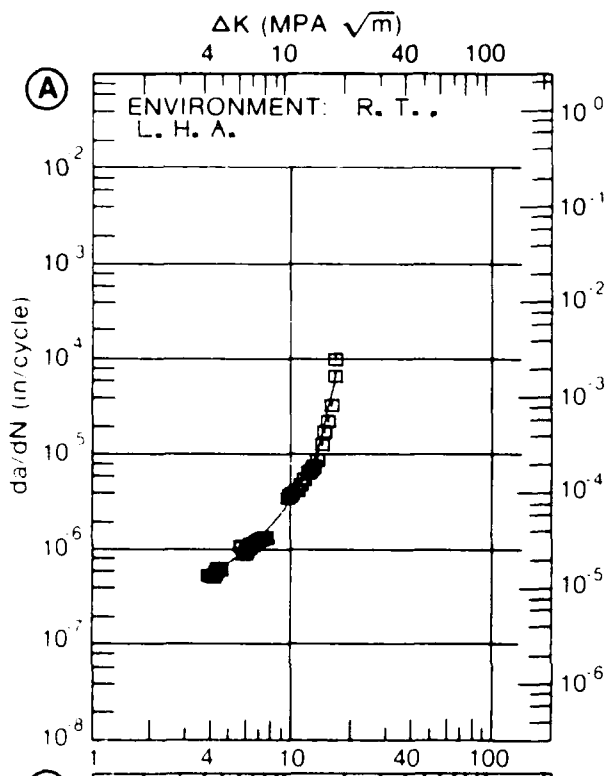


Figure 8.7.3.14

TABLE 8.7.3.15

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.15 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		7050			
CONDITION: T73511					
ENVIRONMENT: R.T. / L.H.A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**+6 IN./CYCLE)			
		A	B	C	D
		R=+0.10	R=+0.50		
DELTA K	A: 3.16	0649			
MIN	B: 1.30		.0133		
	C:				
	D:				
	1.60		.0268		
	2.00		.0496		
	2.50		.0865		
	3.00		.138		
	3.50	.0815	.216		
	4.00	.115	.336		
	5.00	.225	.778		
	6.00	.416	1.61		
	7.00	.723	2.93		
	8.00	1.18	4.77		
	9.00	1.83	7.06		
	10.00	2.71	9.88		
	13.00	7.00	23.3		
	16.00	14.5	52.5		
	20.00	32.0			
	25.00	73.3			
	30.00	190.			
DELTA K	A: 31.94	311.			
MAX	B: 19.47		152.		
	C:				
	D:				
ROOT MEAN SQUARE		17.51	19.61		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1		
SUMMARY	1.25-2.0				
(NP/NA)	02.0				

CONDITION/HT: T73511
 FOPM: 1.80" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 8.00- 50.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.249"
 SPECIMEN WIDTH: 2.500"
 REFERENCES:AL006

ALUM. ALLOY
7050

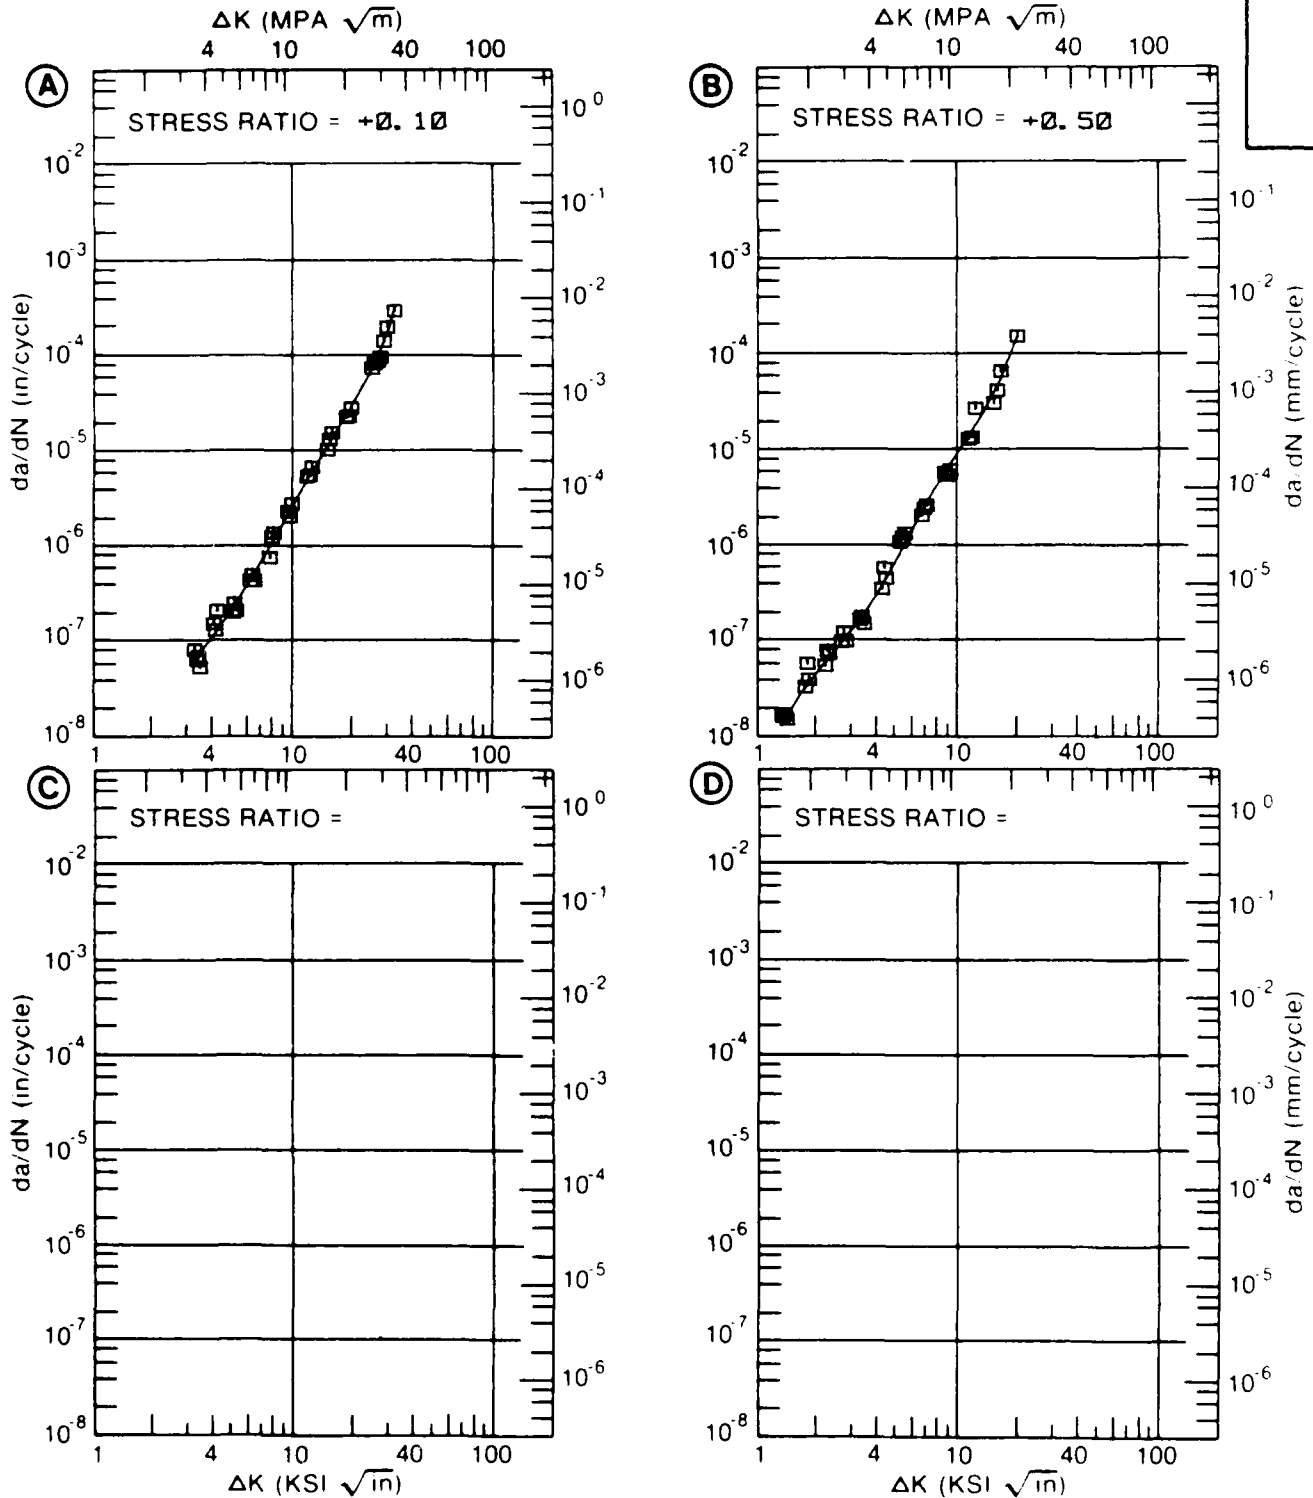


Figure 8.7.3.15

TABLE 8.7.3.16

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.16 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7050
CONDITION: T73511
ENVIRONMENT: R.T., L.H.A.

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=0.33			
DELTA K	A: 4.51	.270			
MIN	B:				
	C:				
	D:				
	5.00	.334			
	6.00	.433			
	7.00	.589			
	8.00	.871			
	9.00	1.34			
	10.00	2.08			
	13.00	7.44			
	16.00	22.8			
DELTA K	A: 17.86	42.1			
MAX	B:				
	C:				
	D:				

ROOT MEAN SQUARE 20.04
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 3
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT T73511
 FORM 1.80" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 7.50- 15.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH
 ULT STRENGTH
 SPECIMEN THK 1.002- 1.003"
 SPECIMEN WIDTH 3.100"
 REFERENCES AL006

ALUM. ALLOY
7050

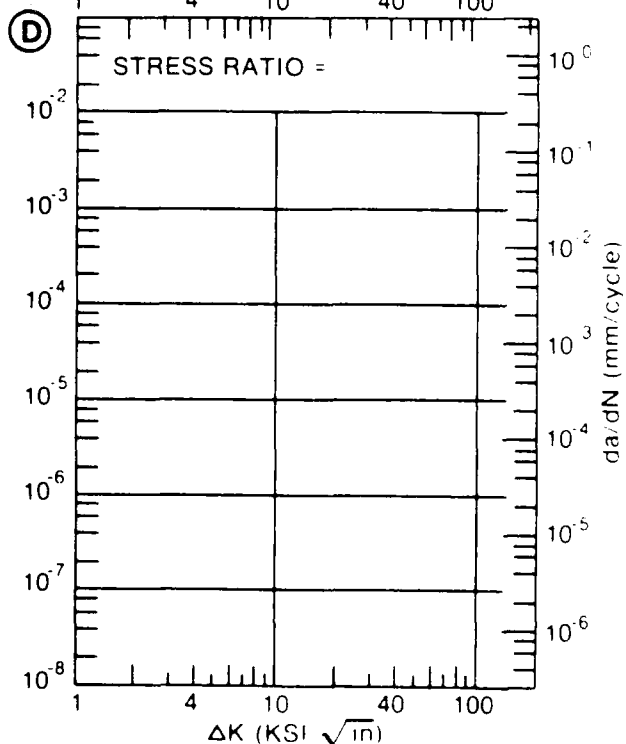
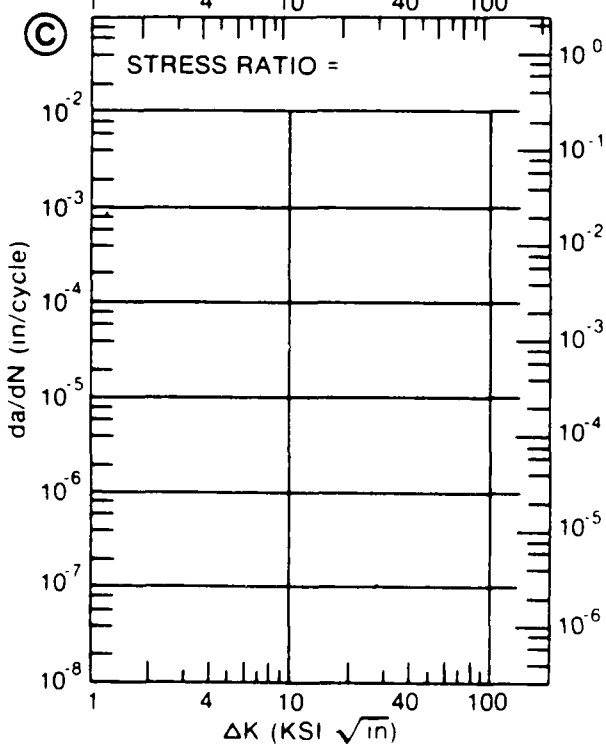
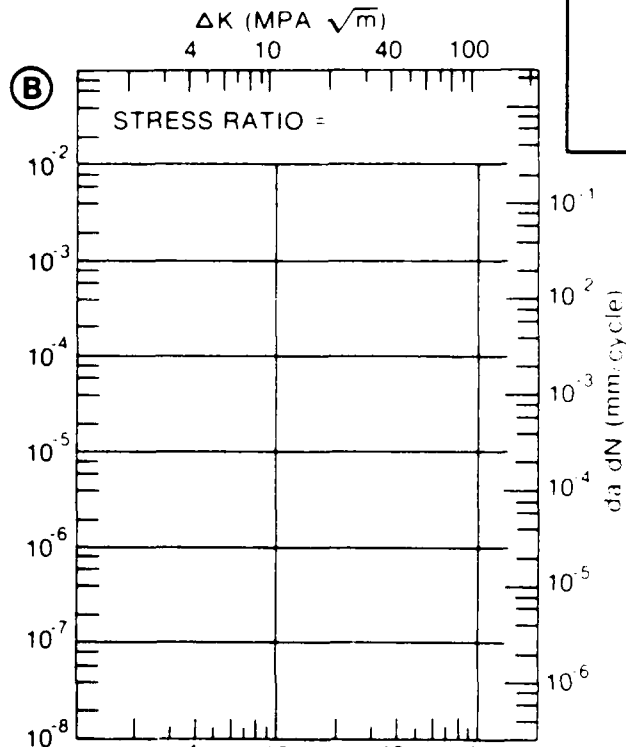
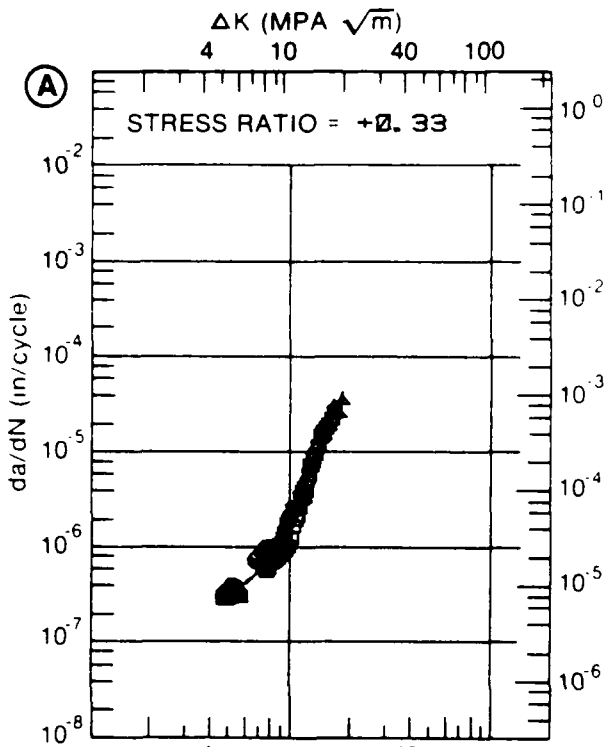


Figure 8.7.3.16

TABLE 8.7.3.17

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.17 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7050
CONDITION: T73511
ENVIRONMENT: R.T. J.H.H.A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		R=+0.33	R=+0.50		
DELTA K	A: 2.72	.121			
MIN	B: 1.33		.00801		
	C:				
	D:				
	1.60		.0307		
	2.00		.0707		
	2.50		.112		
	3.00	.140	.161		
	3.50	.200	.237		
	4.00	.295	.373		
	5.00	.637	1.04		
	6.00	1.28	2.34		
	7.00	2.34	4.00		
	8.00	3.95	5.92		
	9.00	6.15	8.16		
	10.00	8.94	10.9		
	13.00	19.9	25.7		
	16.00	31.0	67.4		
DELTA K	A: 16.62	32.8			
MAX	B: 16.39		77.2		
	C:				
	D:				

ROOT MEAN SQUARE 14.29 21.97
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 3 3
SUMMARY 1.25-2.0
(NP/NA) 2.0

CONDITION/HT: T73511
 FORM: 1.80" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 15.00- 20.00 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.249- 1.000"
 SPECIMEN WIDTH: 2.500- 3.100"
 REFERENCES: AL006

ALUM. ALLOY
7050

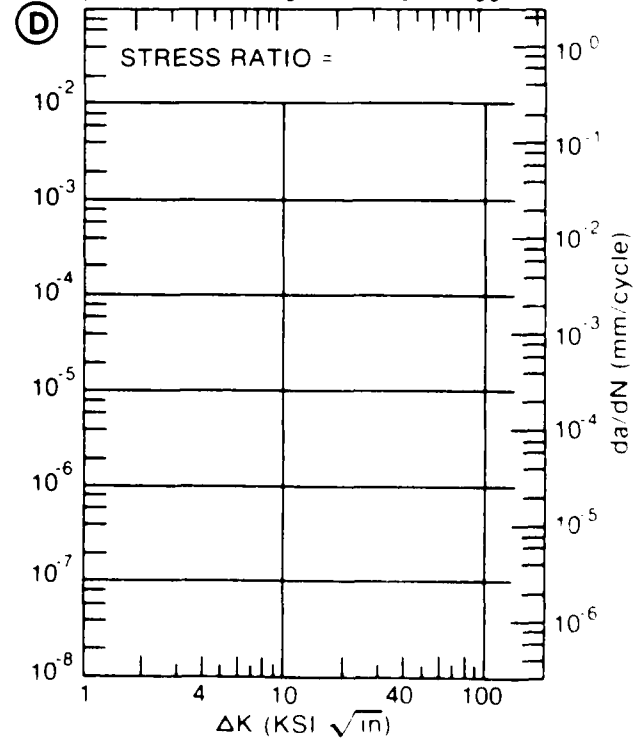
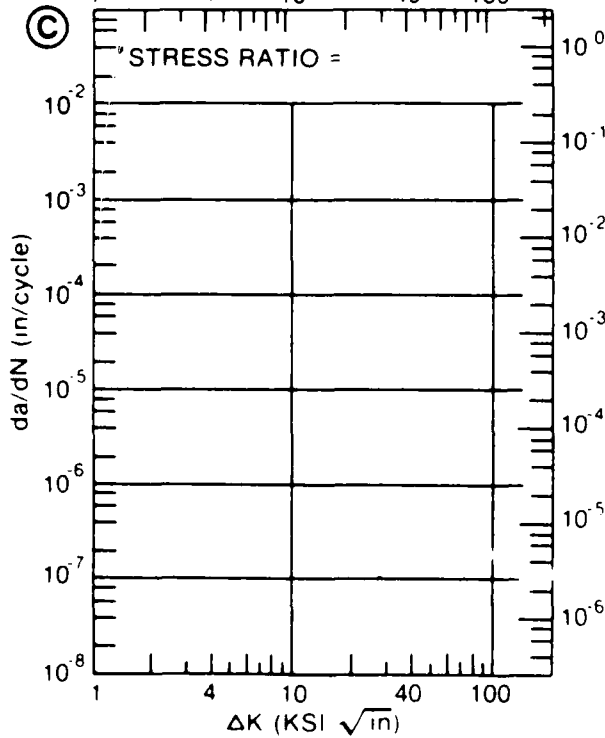
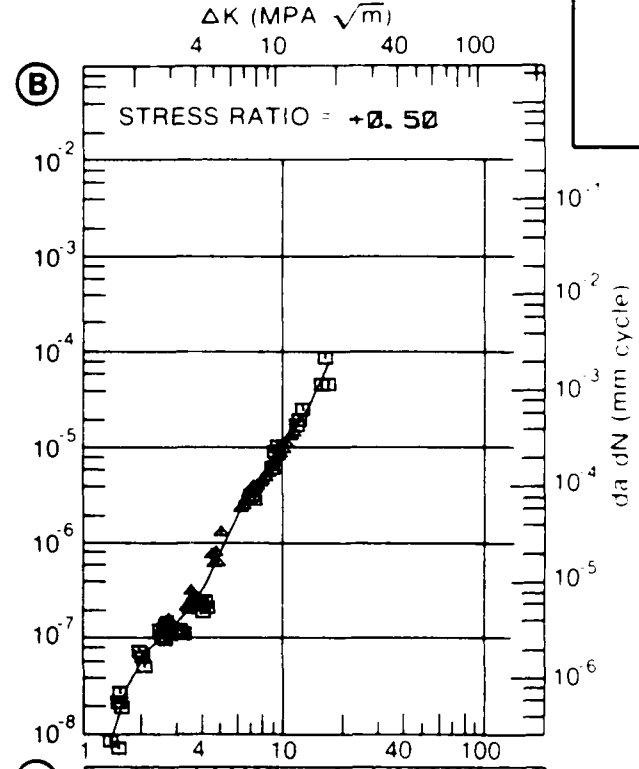
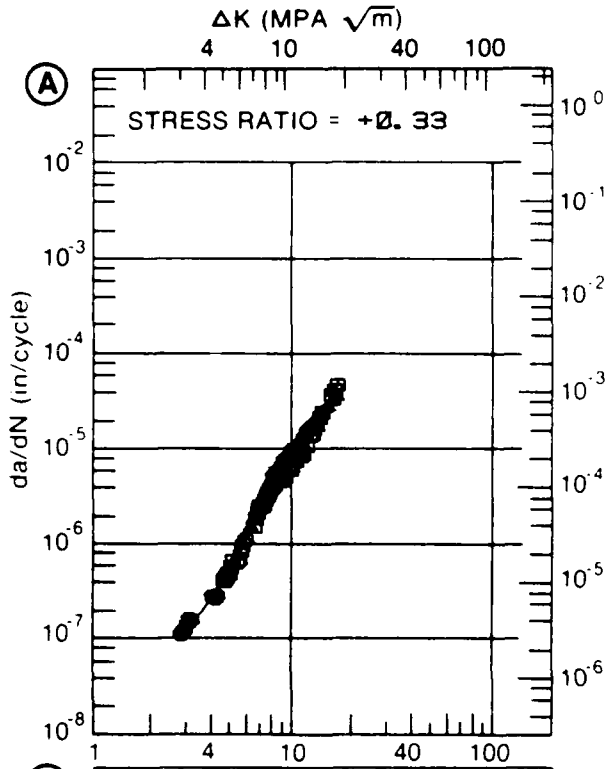


Figure 8.7.3.17

TABLE 8.7.3.18

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.18 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM		7050			
CLNDITION: T73511					
ENVIRONMENT: R T , H II A					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		F(HZ)= 2.00	F(HZ)= 15.00	F(HZ)= 10.00-20.00	F(HZ)= 50.00
DELTA K MIN	A: 7.40	1.76			
	B: 3.31		.119		
	C: 6.68			.796	
	D: 2.62				.011
	3.00				.0268
	3.50		.139		.0528
	4.00		.210		.0783
	5.00		.454		.296
	6.00		.890		
	7.00		1.59	1.11	
	8.00	2.39	2.63	2.35	
	9.00	3.69	4.04	3.75	
	10.00	5.31	5.85	5.16	
	13.00	12.3	13.4	10.2	
	16.00	23.0	22.8	20.3	
	20.00	45.5		45.5	
	25.00	94.6			
	30.00	183			
	35.00	341			
	40.00	619			
	50.00	1664			
DELTA K MAX	A: 53.47	5381			
	B: 16.26		23.6		
	C: 23.95			80.6	
	D: 5.55				634
ROOT MEAN SQUARE		14.59	6.94	10.17	21.61
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	1	1	1	
	1.25-2.0				1
	>2.0				

CONDITION/HT: T73511
 FORM: 1.80" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.154- 0.249"
 SPECIMEN WIDTH: 2.500- 3.000"
 REFERENCES: 86844, AL004, AL006

ALUM.
 ALLOY
 7050

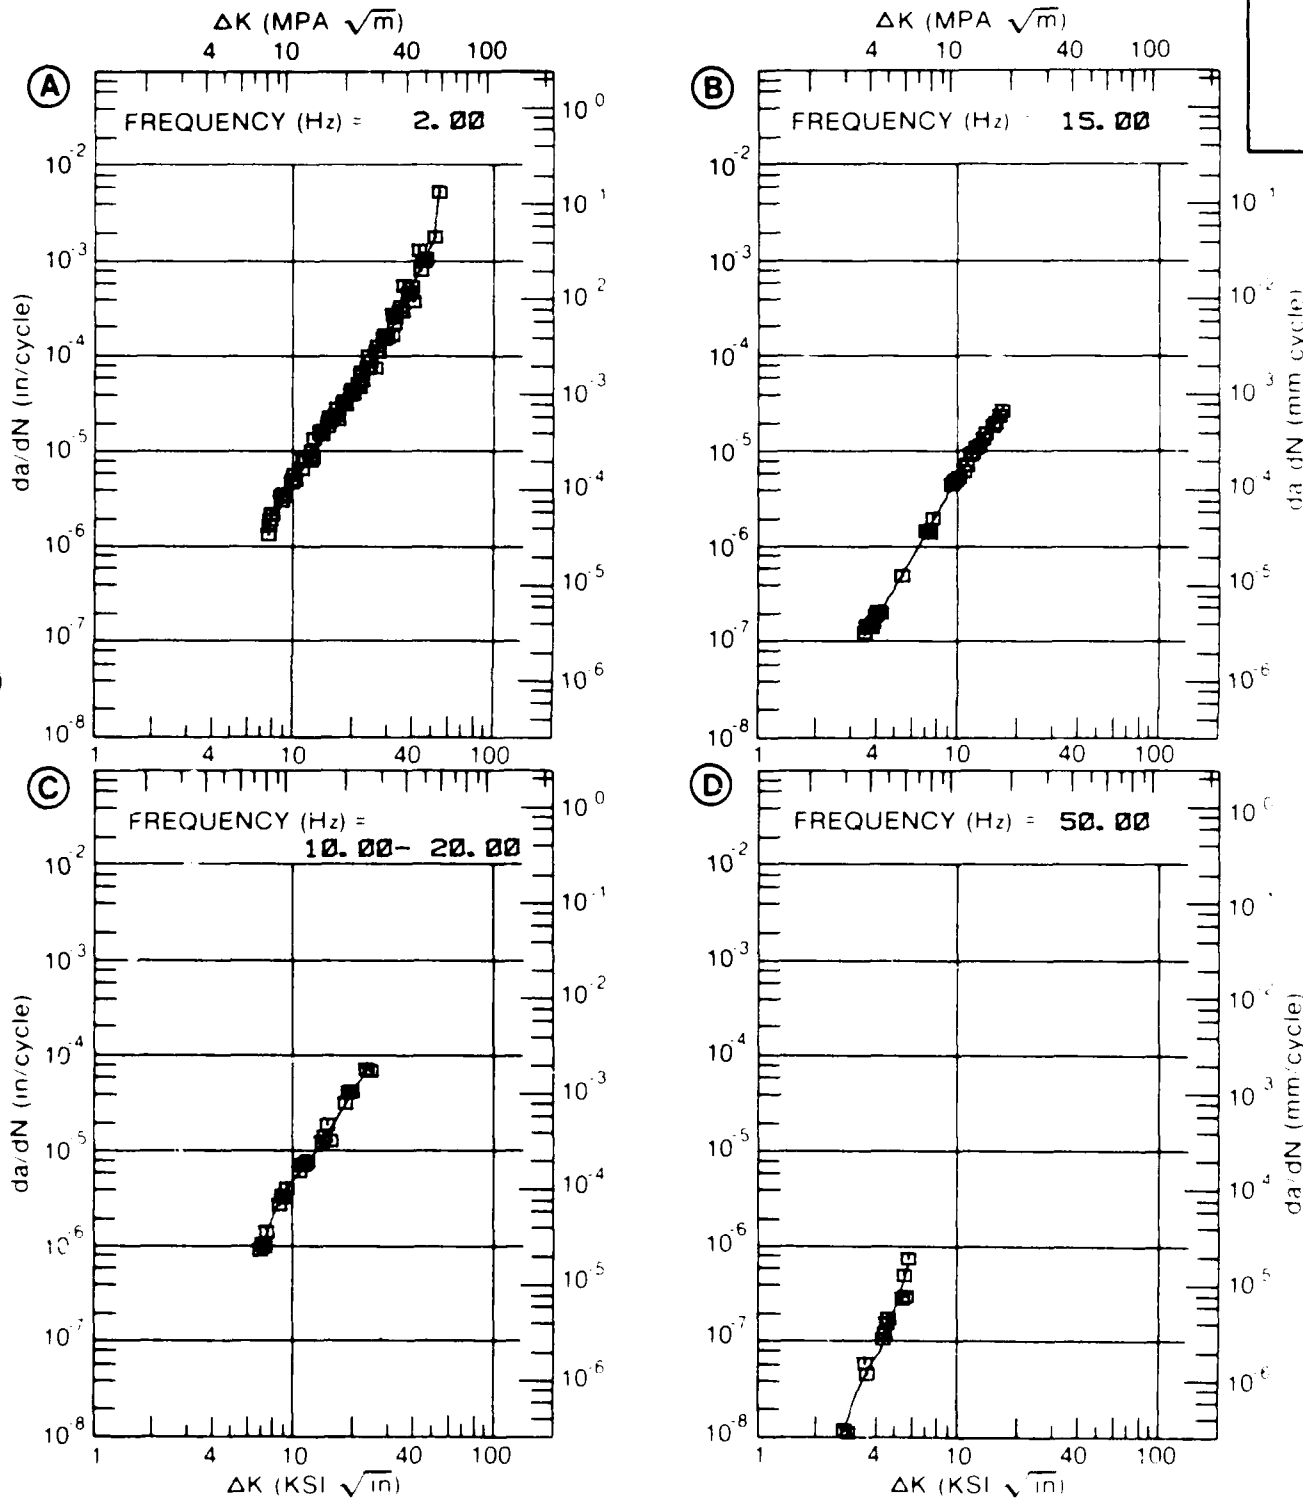


Figure 8.7.3.18

TABLE 8.7.3.19

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.19 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73511					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.		
DELTA K	A: 2.58	.094			
MIN	B: 2.75		.038		
	C: 0				
	D:				
	3.00	.124	.0558		
	3.50	.180	.126		
	4.00	.262	.262		
	5.00	.538	.855		
	6.00	1.03	2.03		
	7.00	1.82	3.82		
	8.00	3.01	6.20		
	9.00	4.67	9.10		
	10.00	6.84	12.4		
	13.00	16.8	23.9		
	16.00	30.7			
DELTA K	A: 17.22	37.0			
MAX	B: 14.82		31.5		
	C:				
	D:				
ROOT MEAN SQUARE		22.14	17.00		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	7	6		
SUMMARY	1.25-2.0		1		
(NP/NA)	2.0				

CONDITION/HT: T73511
 FORM: 1.80" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 7.50- 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.998- 1.004"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL006, AL004, AL007

ALUM.
 ALLOY
 7050

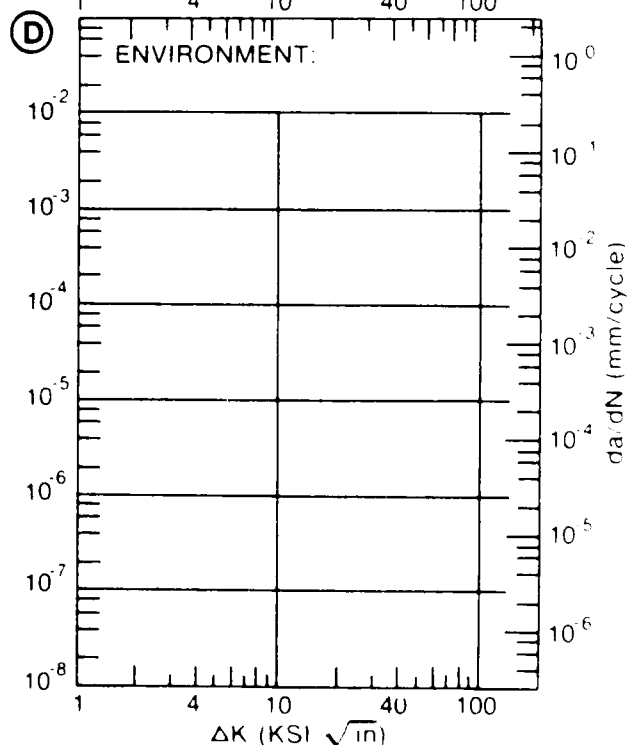
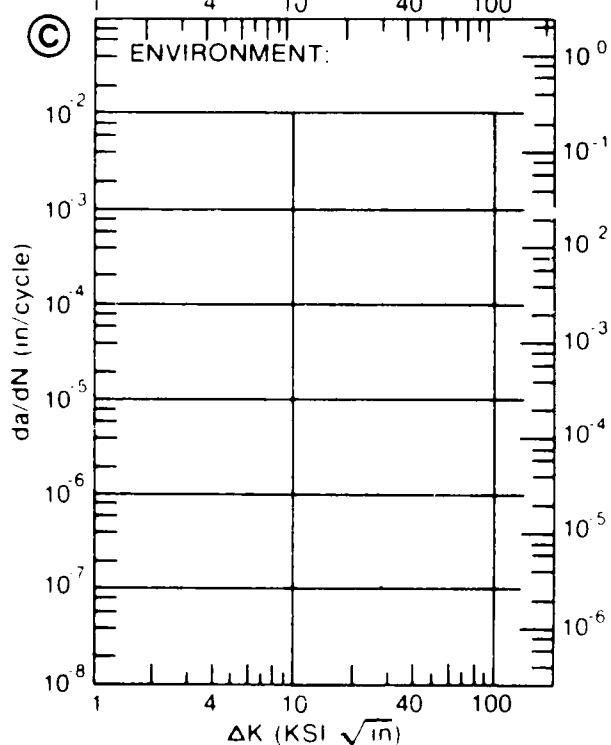
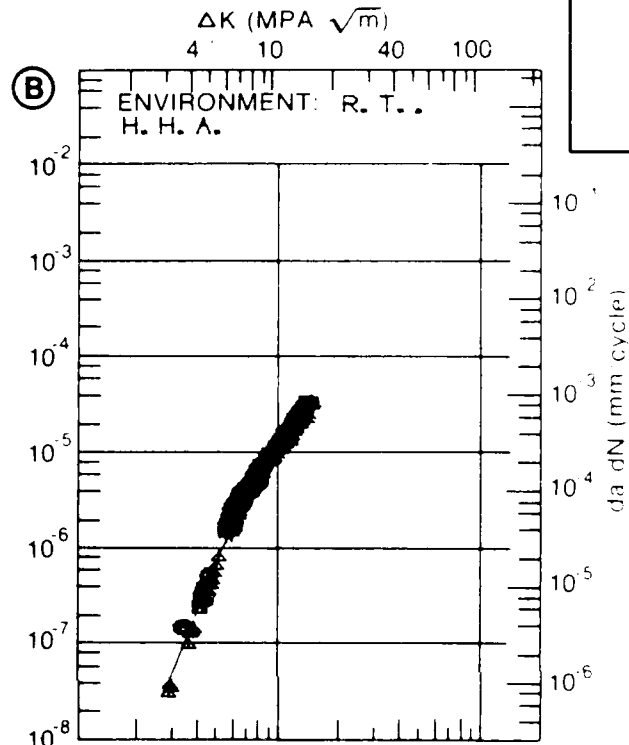
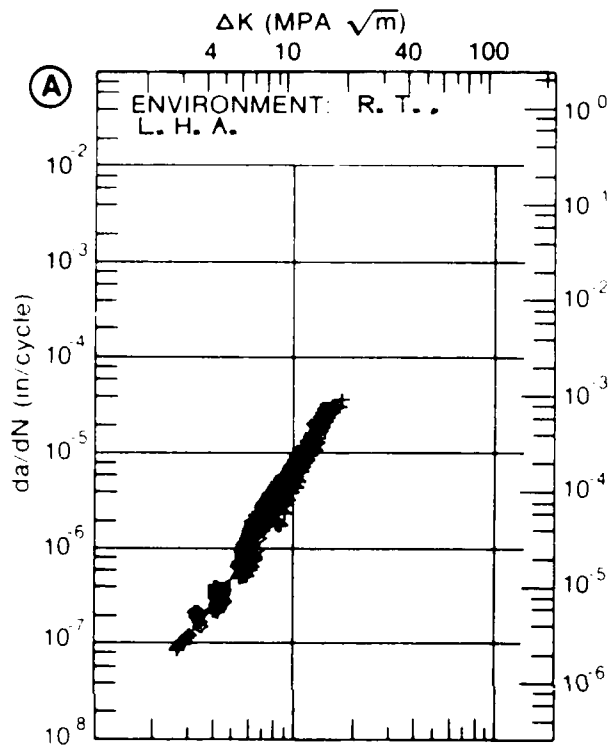


Figure 8.7.3.19

TABLE 8.7.3.20

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.20 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73511

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R. T. L. H. A	E= R. T. H. H. A		
A: 1.83	.023			
DELTA K B: 1.78		.006		
MIN C: 64				
D:				
2.00	.0319	.0194		
2.50	.0613	.0650		
3.00	.0957	.116		
3.50	.136	.183		
4.00	.185	.296		
5.00	.279	.769		
6.00	.46	1.82		
7.00	1.07	3.79		
8.00	1.99	7.05		
9.00	3.71	11.8		
10.00	6.54	17.9		
13.00	21.0	40.8		
16.00	46.8			
A: 18.10	172.			
DELTA K B: 15.39		61.2		
MAX C:				
D:				

ROOT MEAN SQUARE 18.08 24.27
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1 2
SUMMARY 1.25-2.0 1
(NP/NA) 2.0

CONDITION: HT T73511
 FORM 1.80" TH EXTRUSION
 SPECIMEN TYPE CT
 ORIENTATION T-L
 STRESS RATIO +0.50
 FREQUENCY 10.00- 40.00 HZ

YIELD STRENGTH:
 ULT STRENGTH:
 SPECIMEN THK 0.243- 0.999"
 SPECIMEN WIDTH 2.500- 3.805"
 REFERENCES AL006, AL004

ALUM.
ALLOY

7050

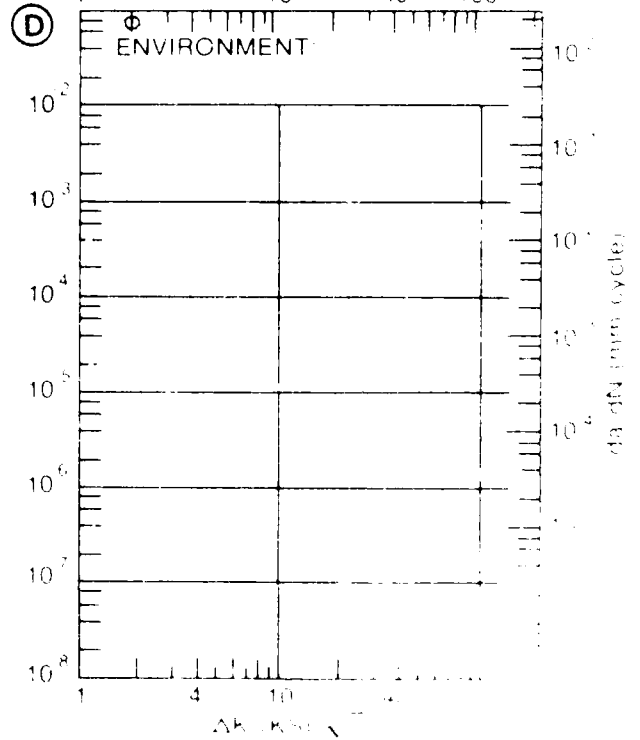
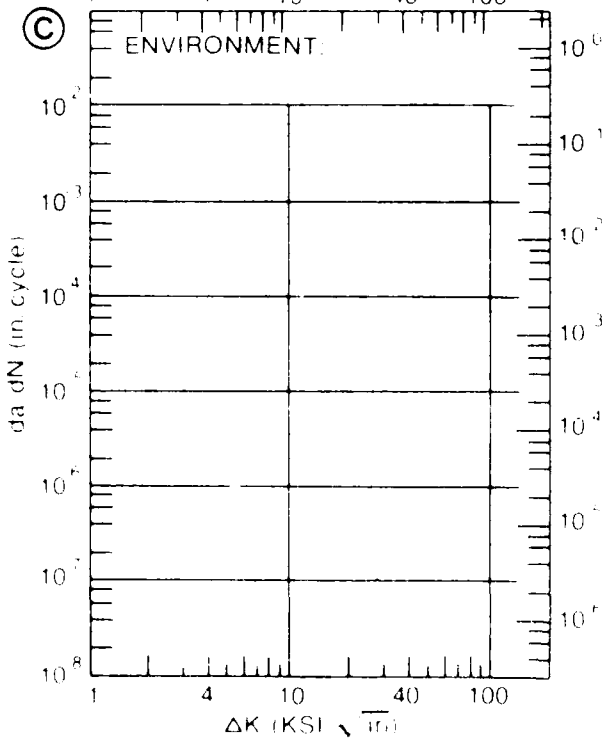
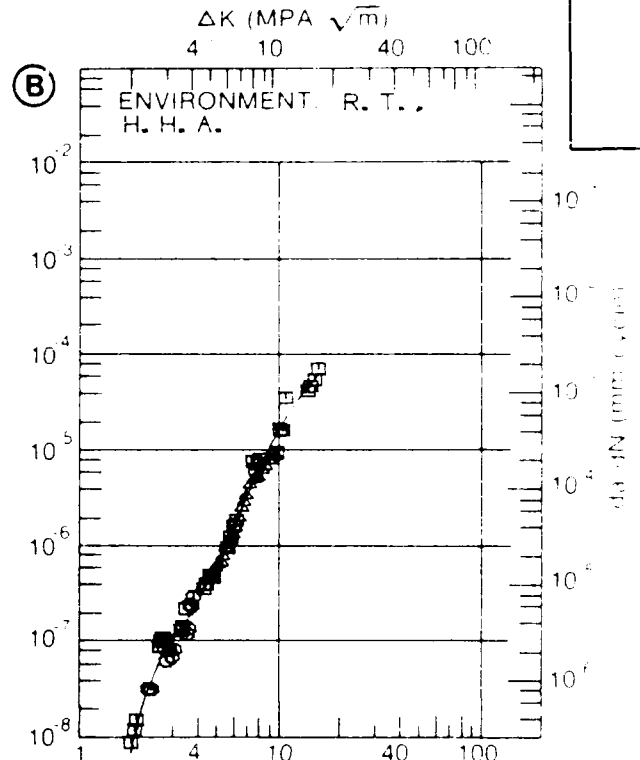
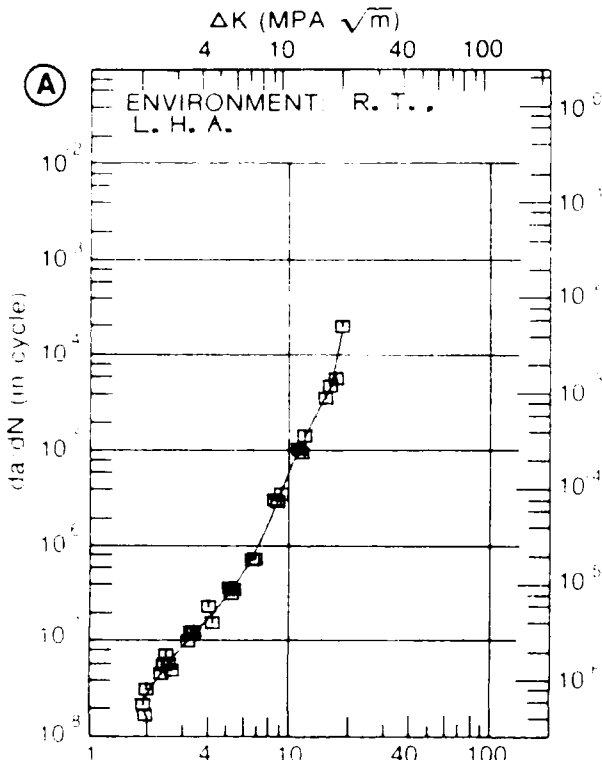


Figure 3.7.12

TABLE 8.7.3.21

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.21 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73511-HIGH PURITY

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR	E= R. T. H. H. A.		
DELTA K MIN	A: 5.87 : B: 5.85 : C: D:	. 505	. 524	
	6.00 : 7.00 : 8.00 : 9.00 : 10.00 : 13.00 : 16.00 :	. 505 . 855 2. 24 4. 18 5. 93 9. 22 26. 7	. 730 2. 85 5. 41 8. 53 12. 2 26. 0 41. 8	
DELTA K MAX	A: 16.48 : B: 19.25 : C: D:	36.0	51.7	

ROOT MEAN SQUARE PERCENT ERROR 22.13 9.79

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73511-HIGH PURITY
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 72.1 KSI
 ULT. STRENGTH: 80.3 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM. ALLOY
7050

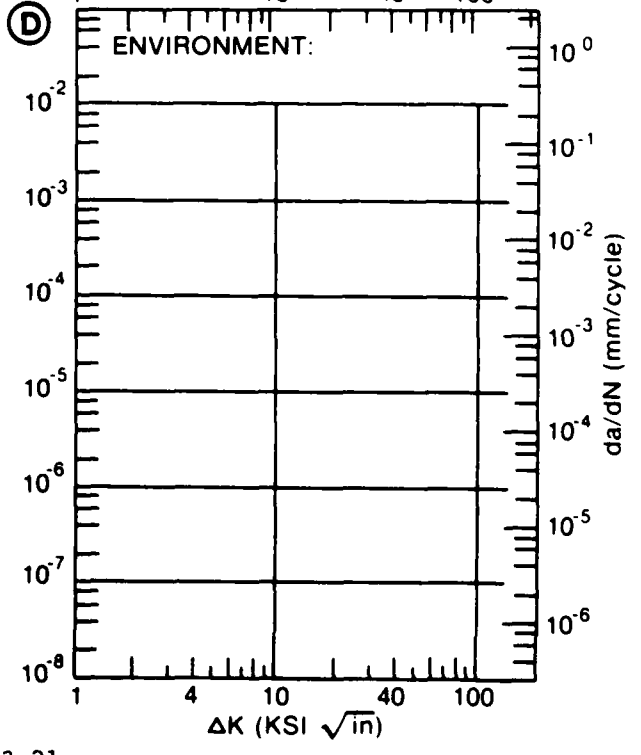
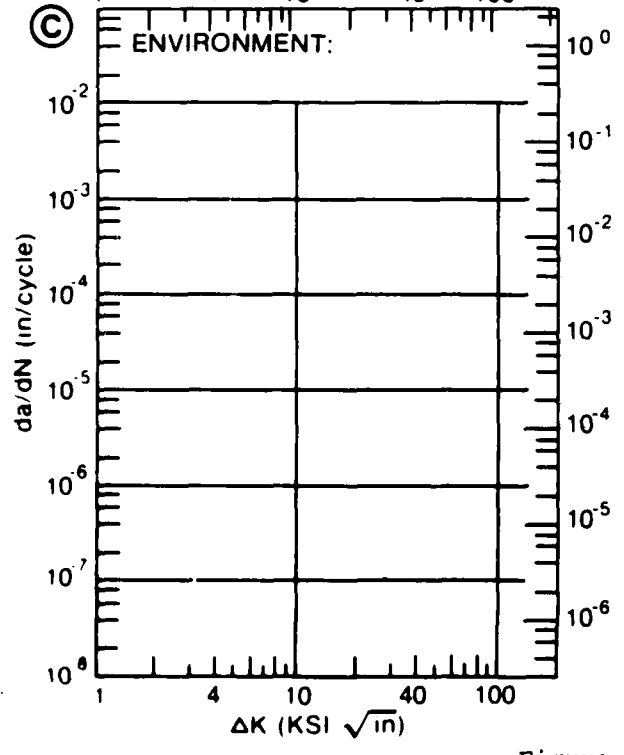
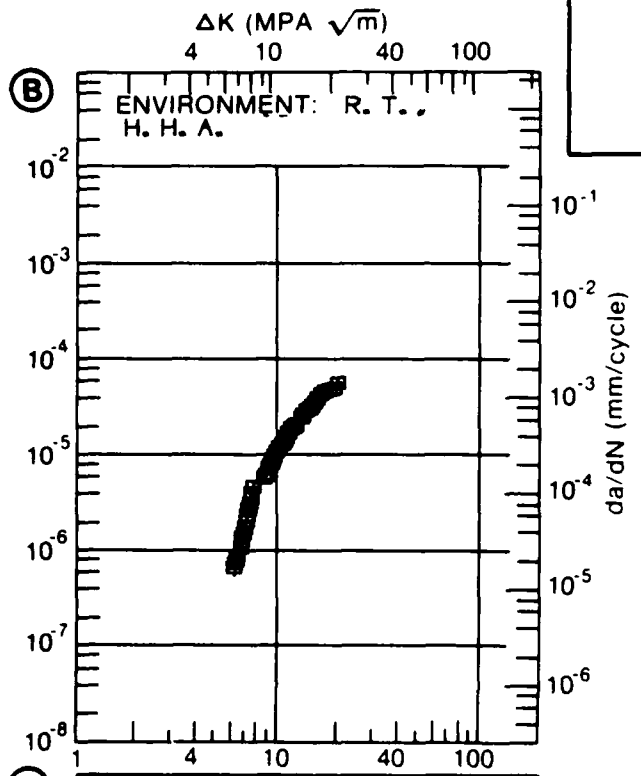
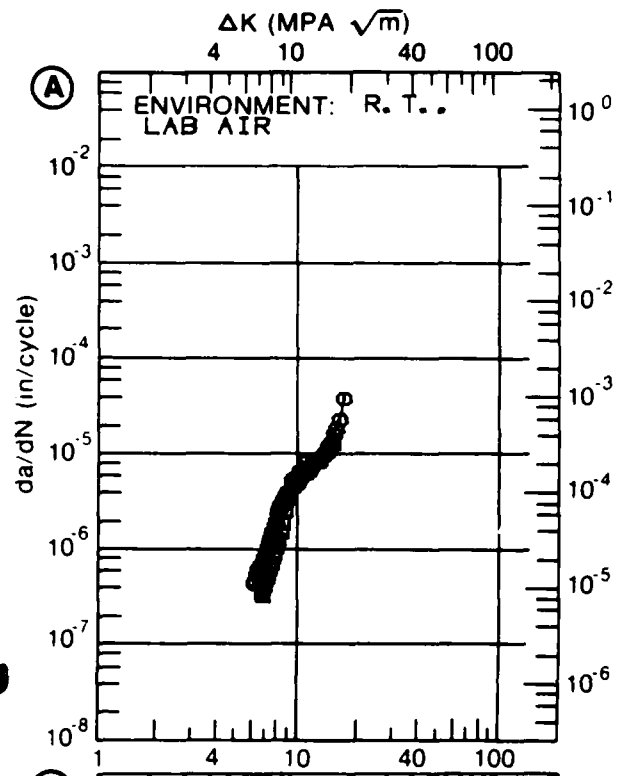


Figure 8.7.3.21

TABLE 8.7.3.22

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.22 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73511-HIGH PURITY

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR			
DELTA K MIN	A: 6.09	.684			
	B:				
	C:				
	D:				
	7.00	1.26			
	8.00	2.03			
	9.00	2.92			
	10.00	3.97			
	13.00	9.19			
	16.00	23.0			
DELTA K MAX	A: 19.26	73.0			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 11.73
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73511-HIGH PURITY
 FORM: 1.50" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 30.00 HZ

YIELD STRENGTH: 66.6 KSI
 ULT. STRENGTH: 75.5 KSI
 SPECIMEN THK: 0.625"
 SPECIMEN WIDTH: 2.550"
 REFERENCES: WA001

ALUM.
ALLOY

7050

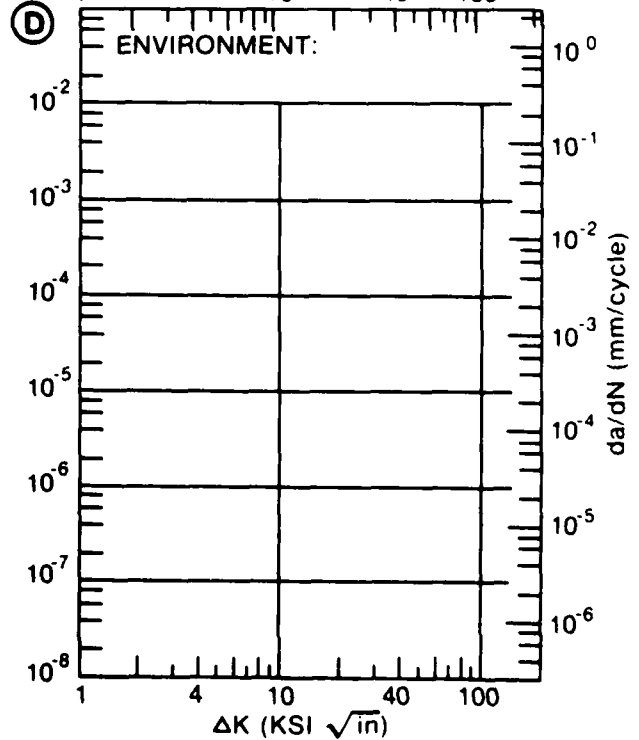
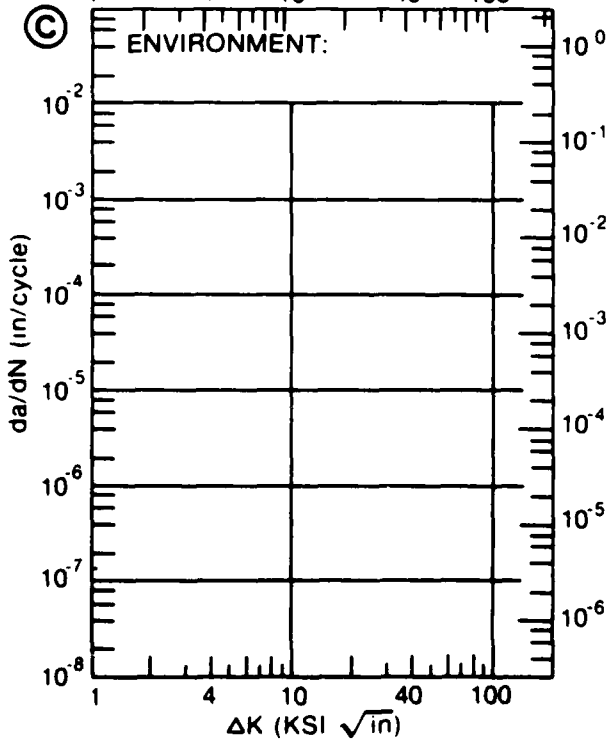
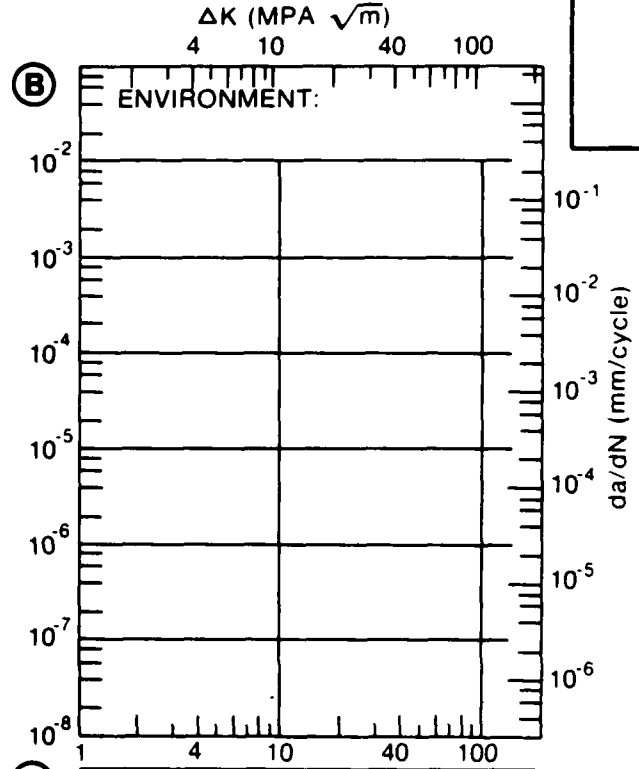
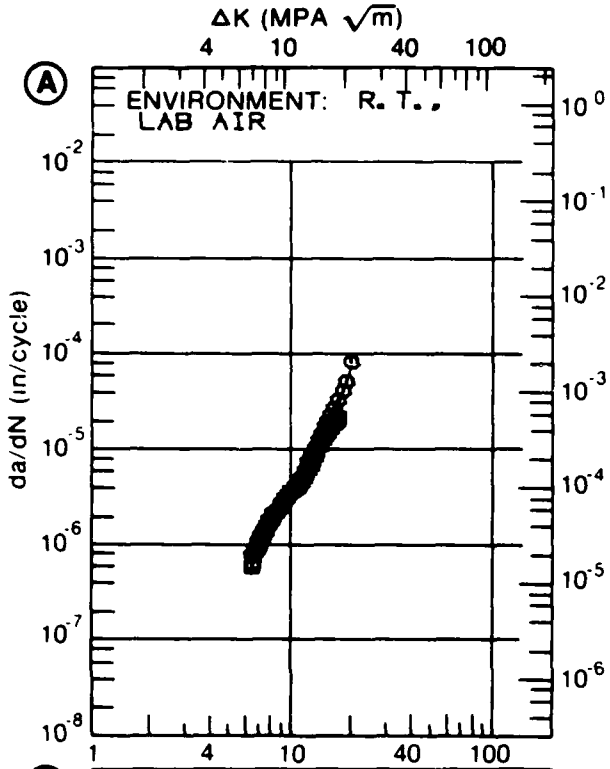


Figure 8.7.3.22

TABLE 8.7.3.23

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.23 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T736					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T.			
		3.5% NaCl			
DELTA K	A: 8.11	9.29			
MIN	B:				
	C:				
	D:				
	9.00	12.4			
	10.00	18.0			
	13.00	38.4			
	16.00	63.4			
DELTA K	A: 19.11	99.6			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		4.77			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T736
 FORM: 1.50" TH FORGING
 SPECIMEN TYPE:
 ORIENTATION:
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91332

ALUM.
ALLOY

7050

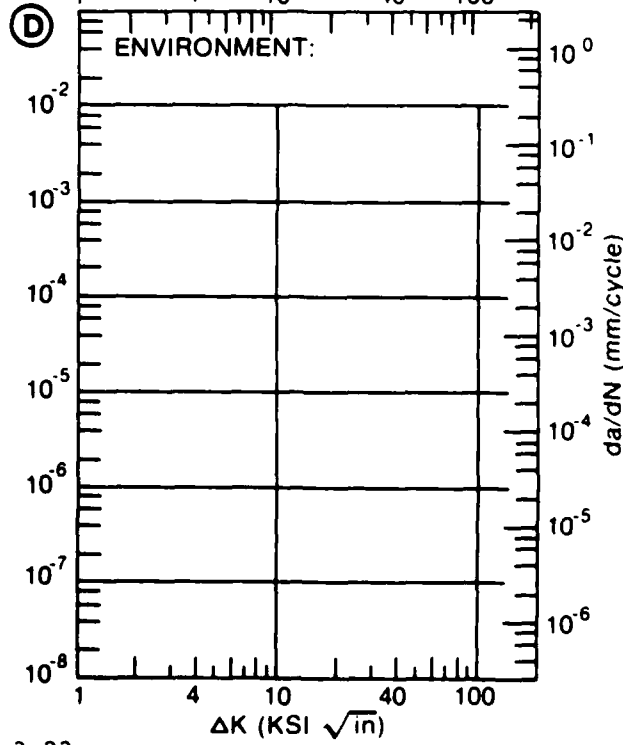
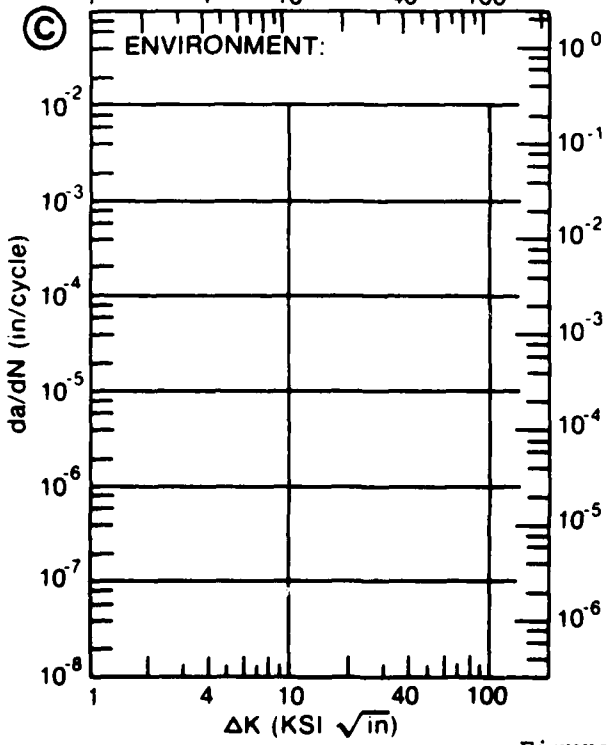
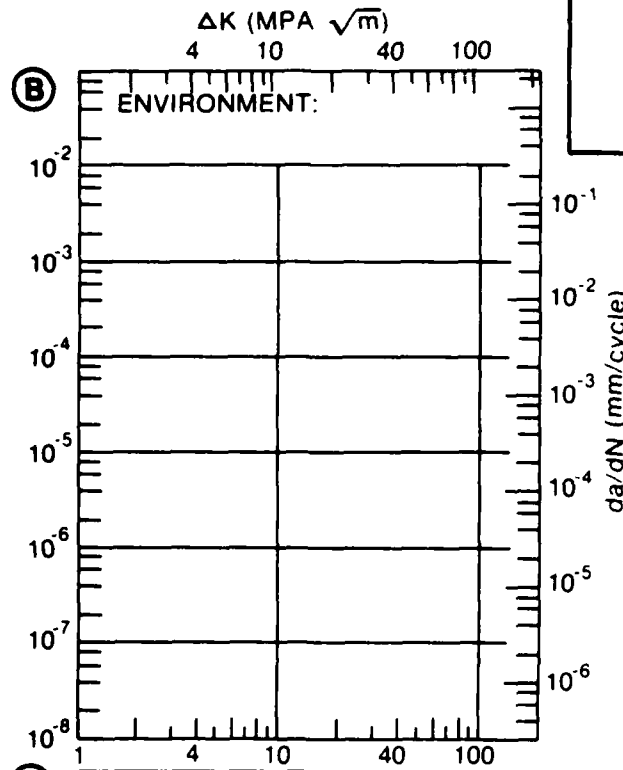
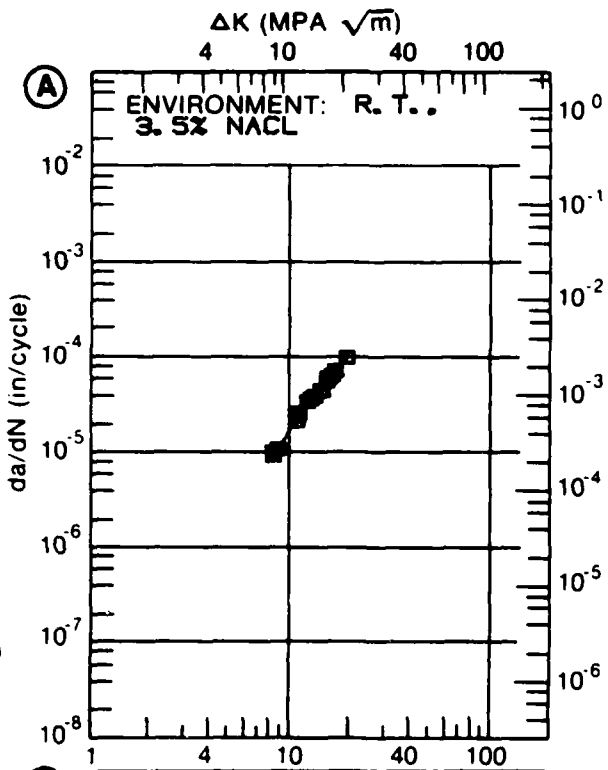


Figure 8.7.3.23

TABLE 8.7.3.24

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.24 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T736					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T.		E= R. T.	
		DRY AIR 20HZ		LAB AIR 3-10HZ	
DELTA K	A: 10.73	1.02			
MIN	B: 6.44		1.90		
	C:				
	D:				
	7.00		2.94		
	8.00		5.40		
	9.00		8.45		
	10.00		11.9		
	13.00	3.69	23.5		
	16.00	11.1	36.6		
	20.00	29.1	58.7		
	25.00	70.7	102.		
	30.00		183.		
	35.00		340.		
DELTA K	A: 25.91	81.7			
MAX	B: 37.11		447.		
	C:				
	D:				
ROOT MEAN SQUARE		7.50	17.53		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25		2		
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T736
 FORM: 1.50- 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY:

YIELD STRENGTH: 63.6 KSI
 ULT. STRENGTH: 72.2 KSI
 SPECIMEN THK: 1.002"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: 91332, NC002

ALUM.
ALLOY

7050

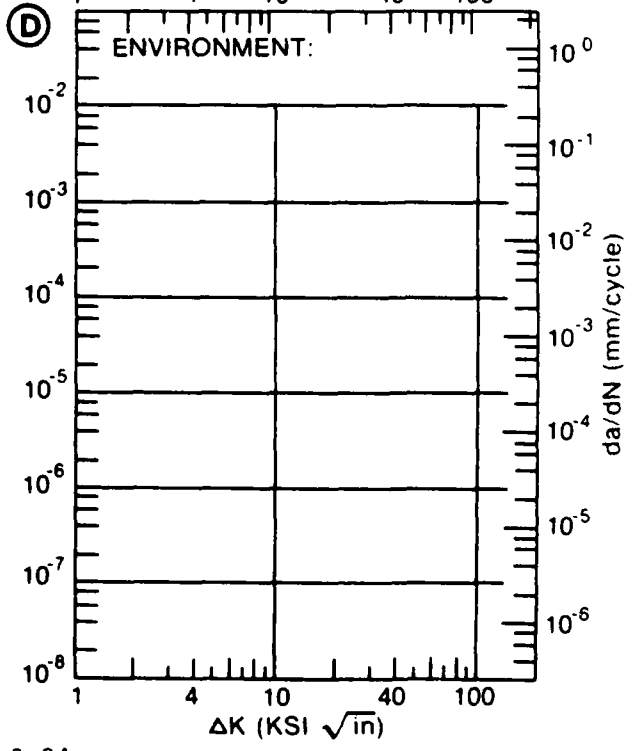
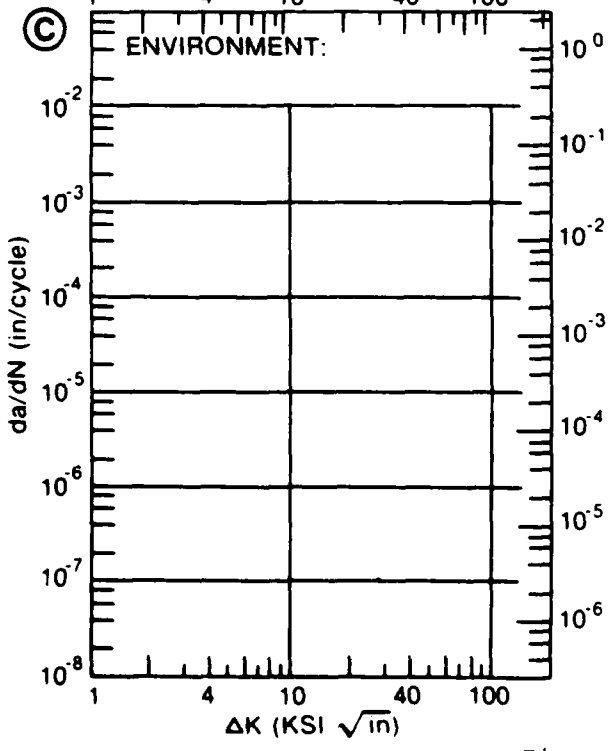
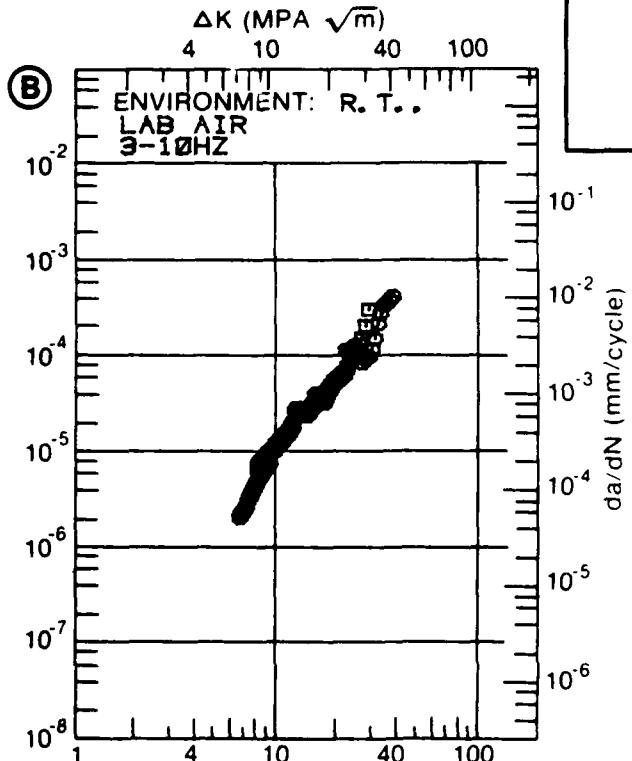
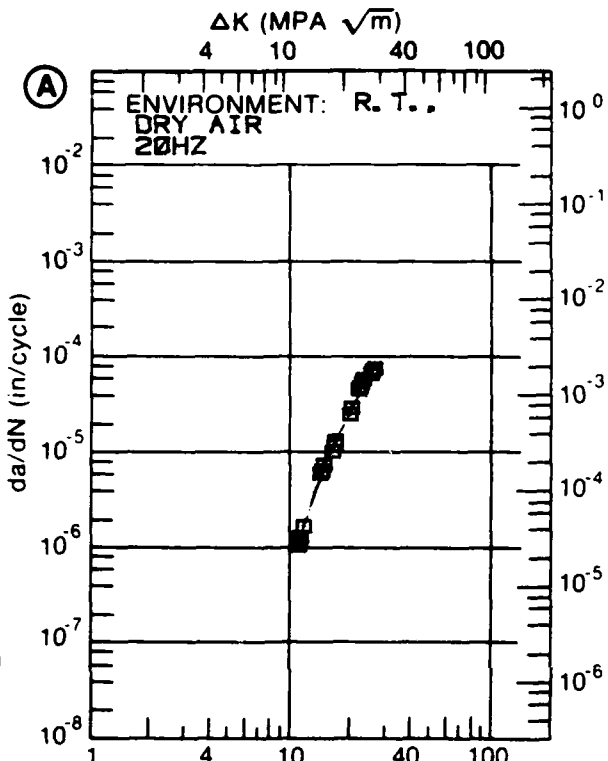


Figure 8.7.3.24

TABLE 8.7.3.25

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.25 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T736

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R. I. LAB AIR			
A: 7.83	1.59			
DELTA K B:				
MIN C:				
D:				
8.00	1.88			
9.00	4.00			
10.00	6.75			
13.00	17.2			
16.00	34.3			
20.00	101.			
A: 23.63	355.			
DELTA K B:				
MAX C:				
D:				

ROOT MEAN SQUARE 11.08
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T736
 FORM: 3.00" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 10.00 HZ

YIELD STRENGTH: 62.2 KSI
 ULT. STRENGTH: 71.5 KSI
 SPECIMEN THK: 1.002"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: NC002

ALUM. ALLOY
7050

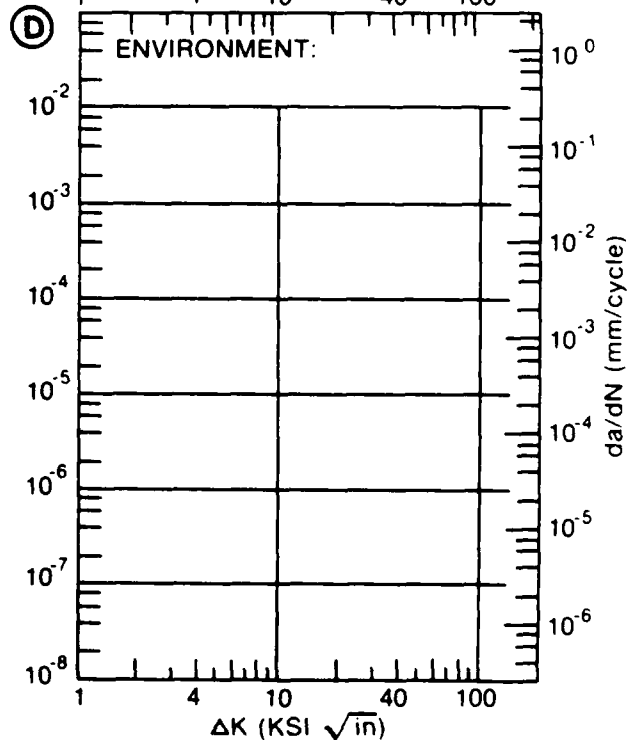
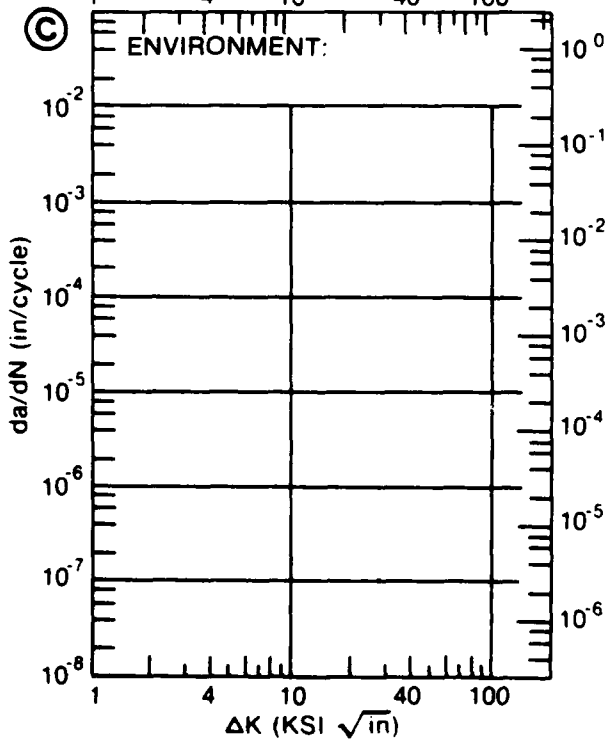
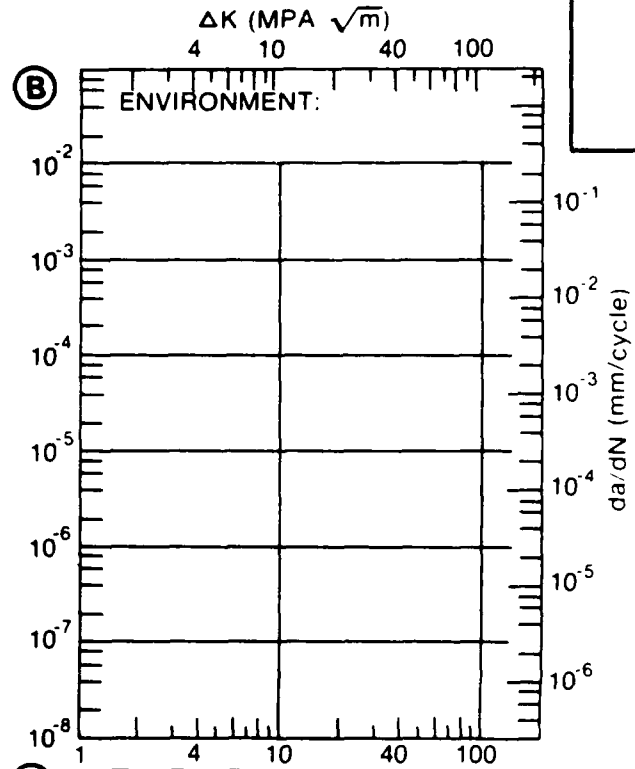
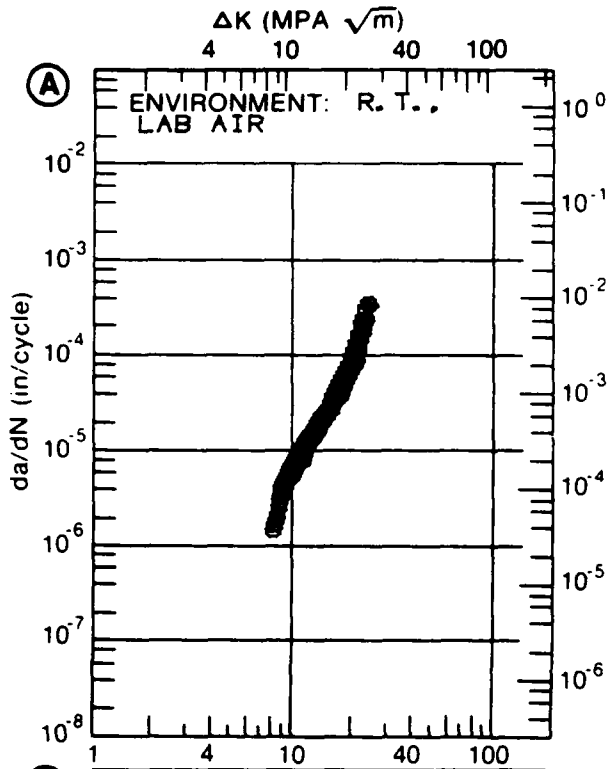


Figure 8.7.3.25

TABLE 8.7.3.26

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.26 INDICATING EFFECT
OF FREQUENCY

MATERIAL: ALUMINUM 7050
CONDITION: T73651
ENVIRONMENT: R. T., 3.5% NaCl

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	F(HZ)= 5.00	F(HZ)= 25.00		
DELTA K MIN	A:	B:	C:	D:
	200.00			
DELTA K MAX	A:	B:	C:	D:
ROOT MEAN SQUARE PERCENT ERROR	0.00	0.00		
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5	0.5-0.8	0.8-1.25	1.25-2.0 >2.0

CONDITION/HT: T73651
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 ENVIRONMENT: R. T., 3.5% NaCl

YIELD STRENGTH: 70.0 KSI
 ULT. STRENGTH: 80.5 KSI
 SPECIMEN THK: 0.750"
 SPECIMEN WIDTH: 1.500"
 REFERENCES: 88174

ALUM.
ALLOY

7050

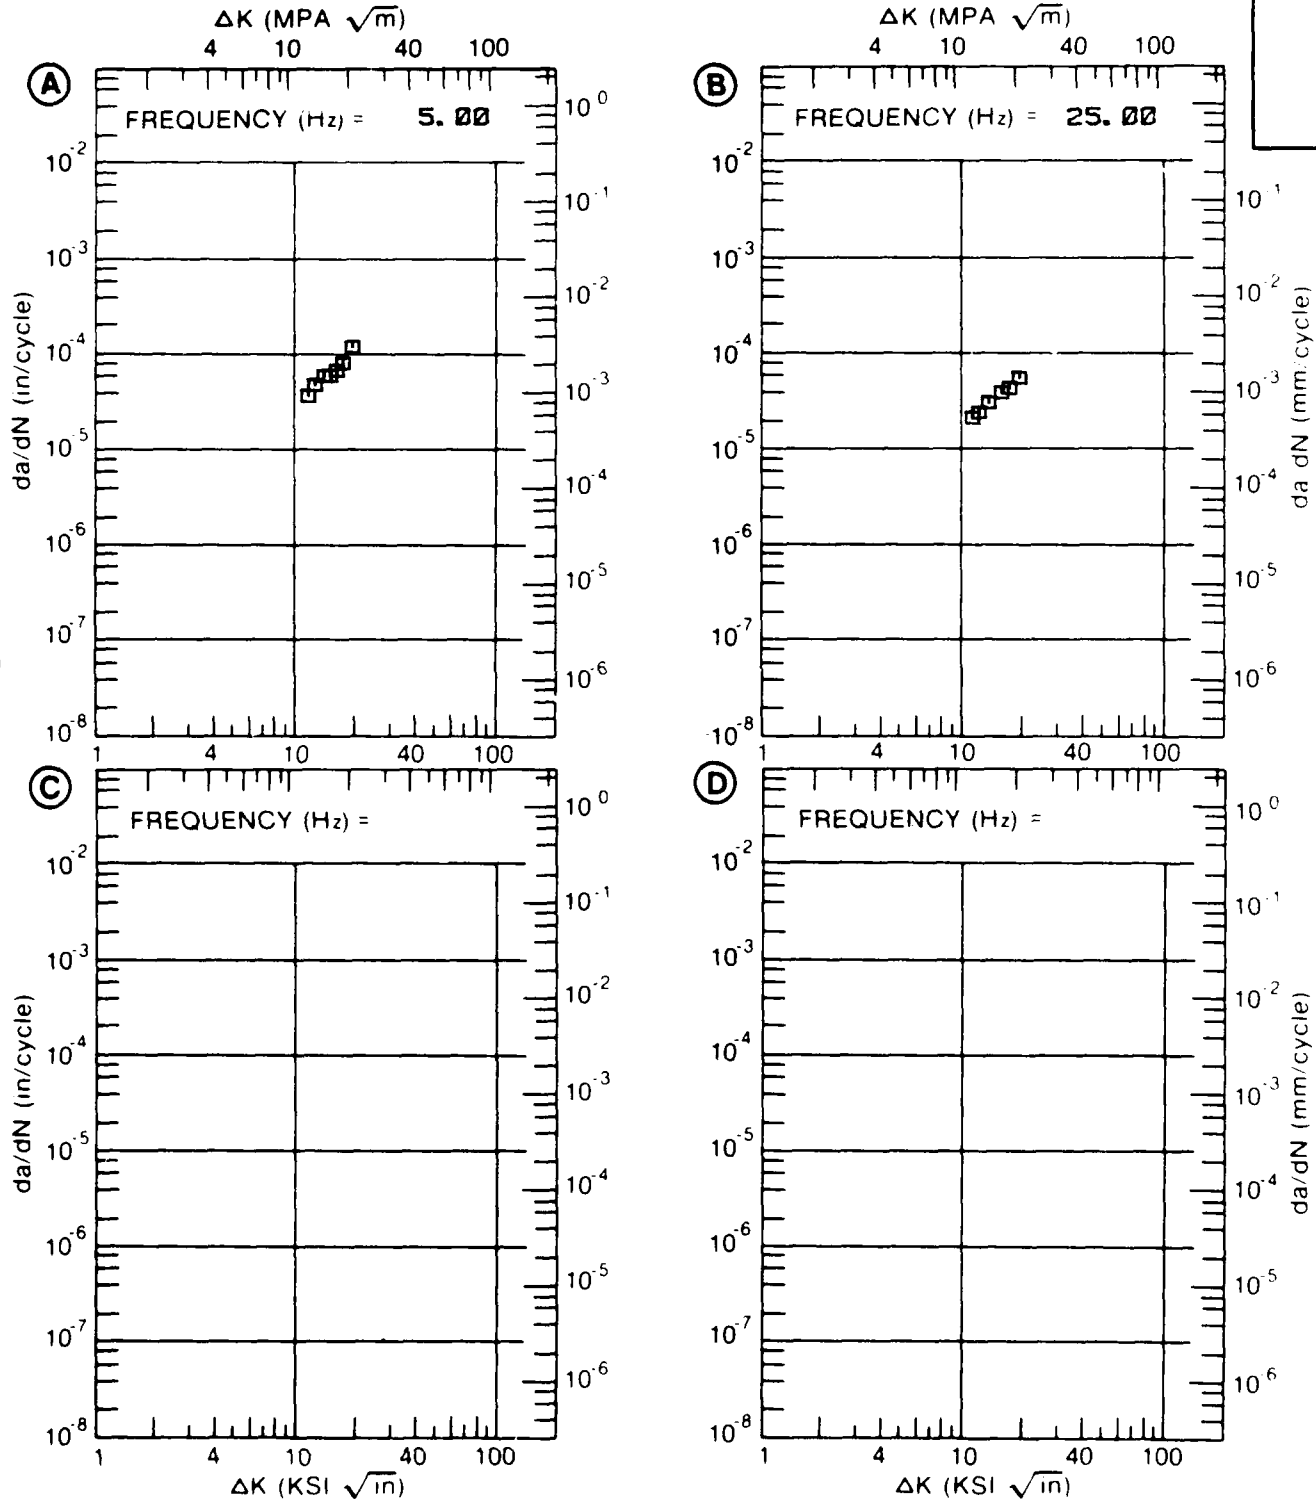


Figure 8.7.3.26

TABLE 8.7.3.27

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.27 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.85	1.99			
	B: 5.81		3.47		
	C: 6.03			8.22	
	D:				
	6.00	2.24	3.88		
	7.00	4.16	6.23	9.63	
	8.00	6.42	8.86	14.6	
	9.00	9.00	11.8	21.6	
	10.00	12.0	15.3	28.5	
	13.00	27.4	31.1	49.3	
	16.00	68.1	65.3		
DELTA K MAX	A: 18.68	173.			
	B: 16.05		66.2		
	C: 15.69			89.1	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		6.72	6.70	9.42	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1	

CONDITION/HT: T73651
 FORM: 1.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 65.4 KSI
 ULT. STRENGTH: 75.1 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.801- 3.805"
 REFERENCES: AL013

ALUM.
 ALLOY
 7050

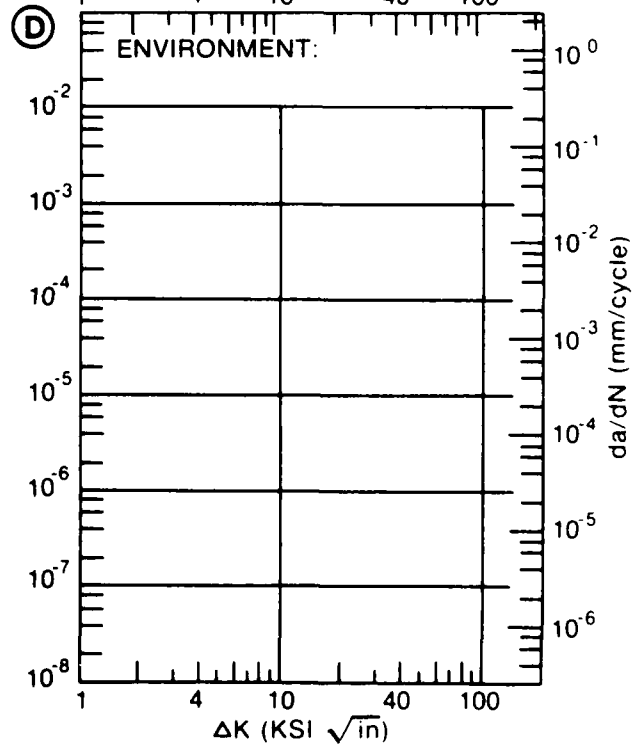
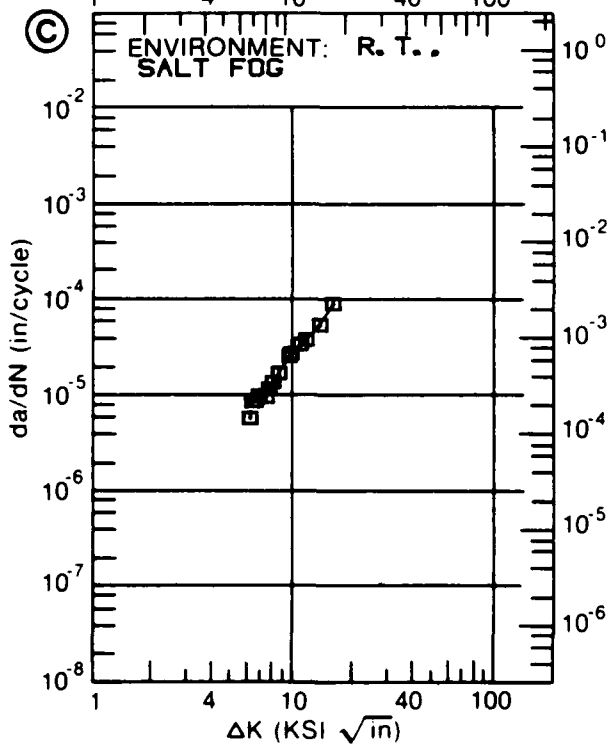
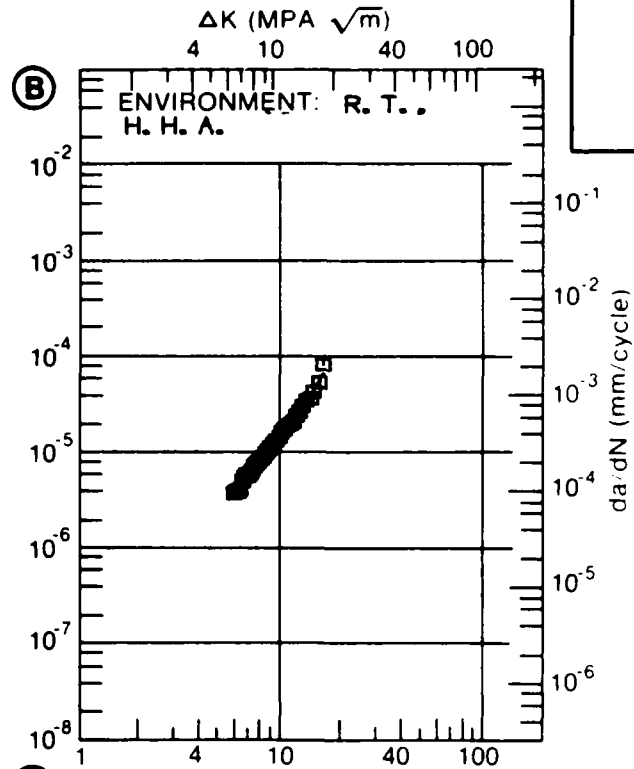
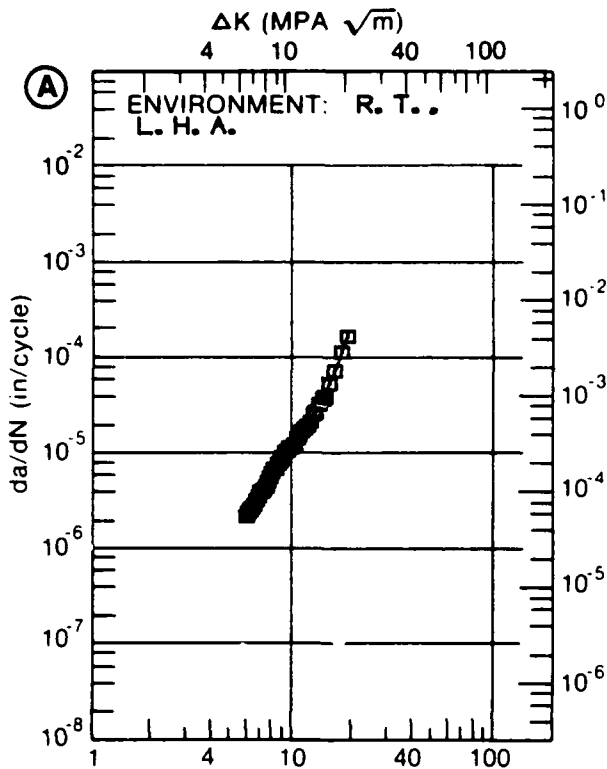


Figure 8.7.3.27

TABLE 1

FATIGUE CRACK GROWTH RATE AS A FUNCTION
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 1 (CONTINUED) WITH
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73651

DELTA K (KSI*IN**1/2)	DA/DN (10**+6 IN /CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR 3-25HZ	E= R. T. S. T. W. 1-10HZ	E= R. T. SIM. SEA WATER 1-10HZ	
DELTA K MIN	A: 4.07	B: 4.735	C: 1.38	D:
	5.00 : .560	1.12	1.49	
	6.00 : 1.10	3.75	3.57	
	7.00 : 1.45	8.19	6.36	
	8.00 : 1.97	12.0	9.69	
	9.00 : 2.79	14.8	13.6	
	10.00 : 4.09	17.5	18.2	
	13.00 : 11.8	29.9	40.4	
	16.00 : 24.4	47.7	83.0	
	20.00 : 48.7	79.3	164.	
	25.00 : 206.	243.	312.	
DELTA K MAX	A: 29.97	B: 306.	C: 1334.	D:
	25.70 : 2303.			
	28.53 : 306.			

ROOT MEAN SQUARE PERCENT ERROR 30.13 13.69 10.61

LIFE PREDICTION RATIO SUMMARY (NP/NA) 0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0

5 2 2

CONDITION/HT T73651
 FORM 1.00- 3.15" TH PLATE
 SPECIMEN TYPE CT
 ORIENTATION L-T
 STRESS RATIO +0.10
 FREQUENCY

YIELD STRENGTH: 65.6- 70.0 KSI
 ULT. STRENGTH: 76.6- 80.5 KSI
 SPECIMEN THK: 0.750- 1.007"
 SPECIMEN WIDTH: 1.500- 7.400"
 REFERENCES: 88174, NC002

ALUM. ALLOY
7050

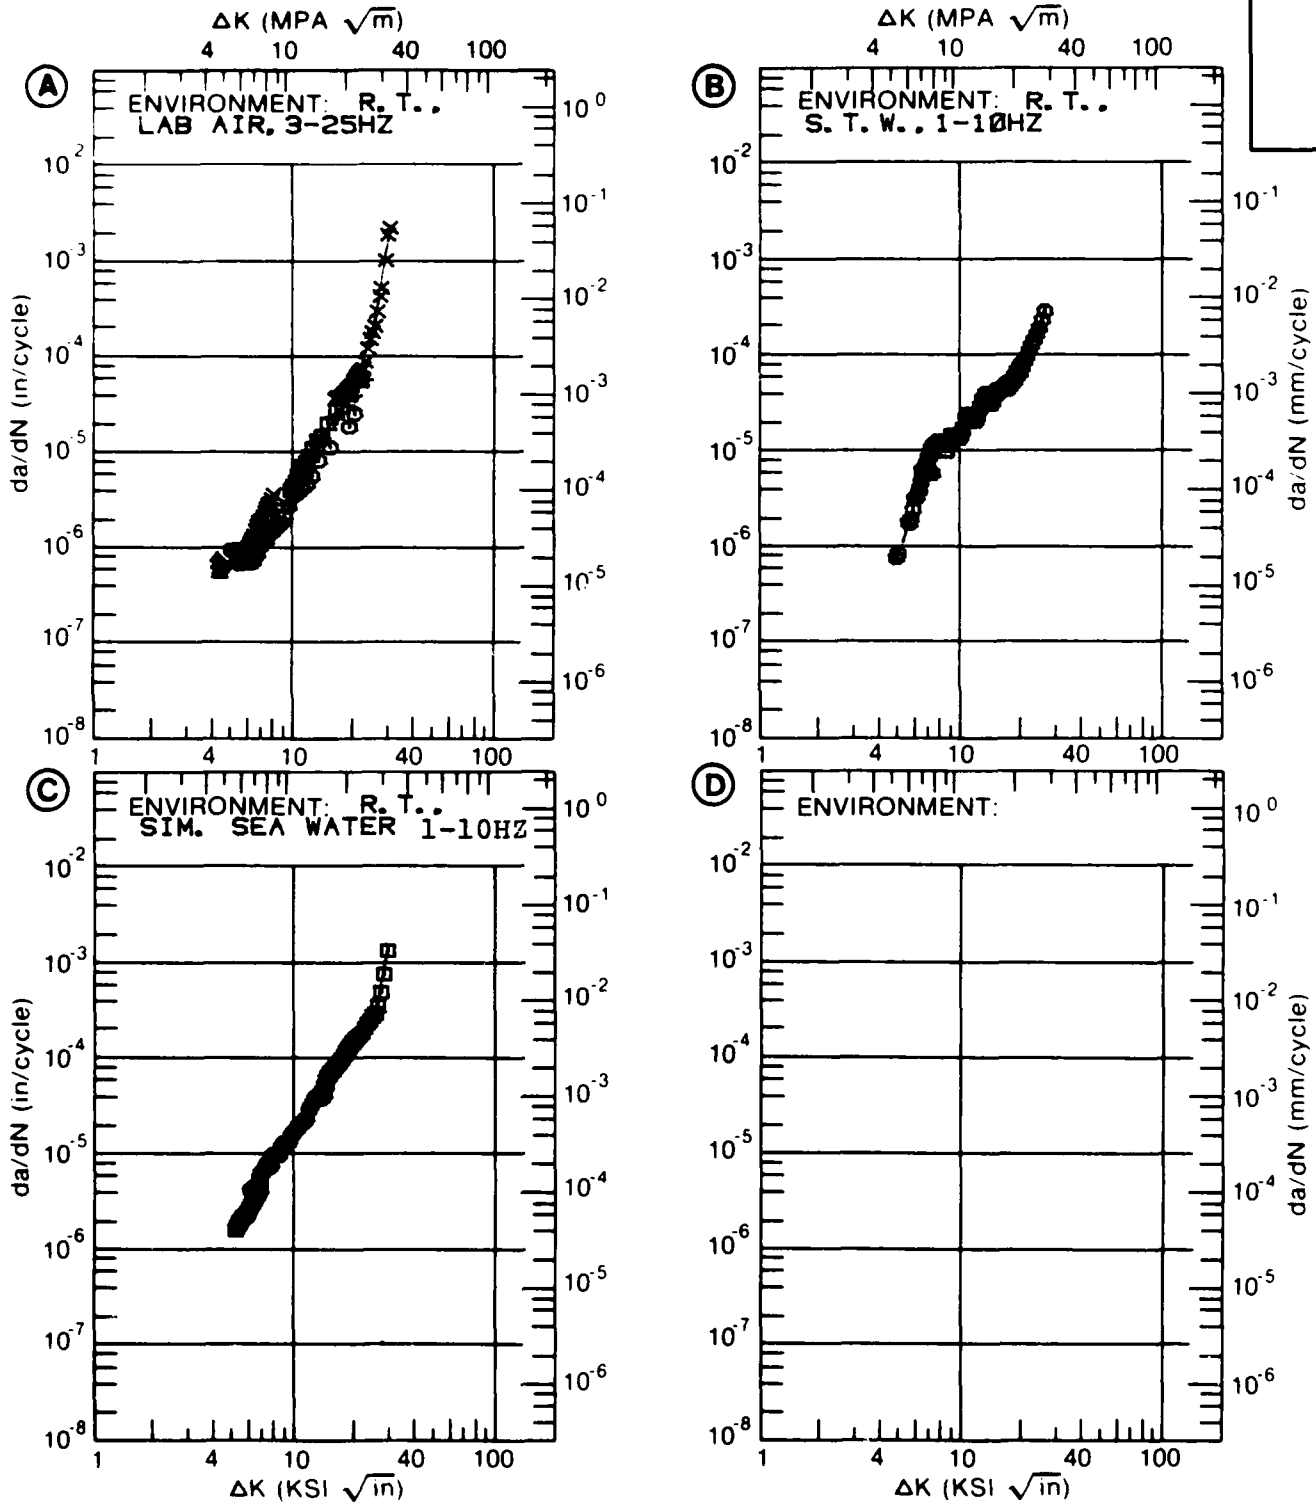


Figure 8.7.3.28

TABLE 8.7.3.29

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.29 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73651

DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. H. H. A.	E= R. T. HHA		
DELTA K	A: 1.96	.014			
MIN	B: 2.72		.100		
	C:				
	D:				
	2.00	.0164			
	2.50	.0600			
	3.00	.157	.144		
	3.50	.334	.257		
	4.00	.613	.431		
	5.00	1.55	1.03		
	6.00	3.09	2.10		
	7.00	5.27	3.76		
	8.00	8.11	6.11		
	9.00	11.6	9.18		
	10.00	15.7	12.9		
	13.00	31.3	27.6		
	16.00	51.1	44.3		
	20.00	82.9	63.3		
	25.00	130.			
	30.00	183.			
DELTA K	A: 30.30	186.			
MAX	B: 20.39		64.8		
	C:				
	D:				

ROOT MEAN SQUARE 21.84 27.63
PERCENT ERROR

LIFE	0.0-0.5		
PREDICTION	0.5-0.8	1	1
RATIO	0.8-1.25	2	1
SUMMARY	1.25-2.0		1
(NP/NA)	>2.0		

CONDITION/HT: T73651
 FORM: 1.00- 5.68" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 25.00 HZ

YIELD STRENGTH: 69.0 KSI
 ULT. STRENGTH: 77.0 KSI
 SPECIMEN THK: 0.243- 0.252"
 SPECIMEN WIDTH: 2.496- 2.550"
 REFERENCES:AL013

ALUM. ALLOY
7050

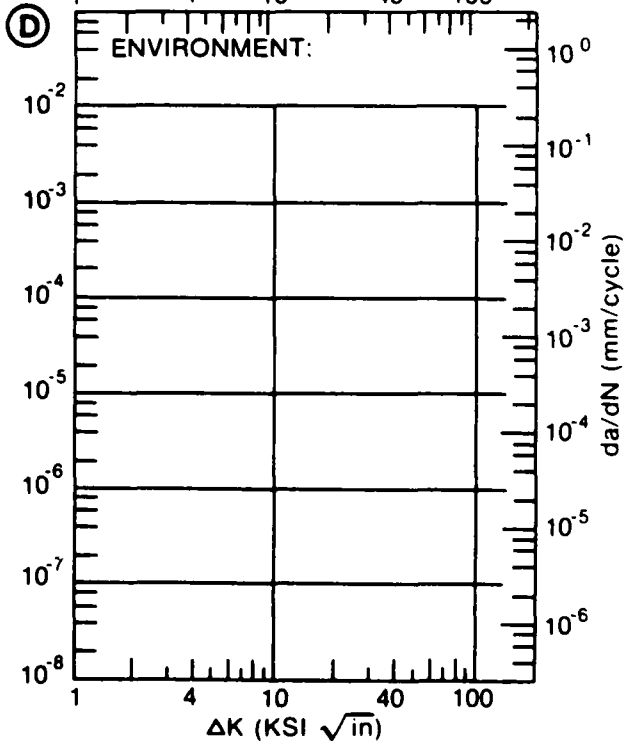
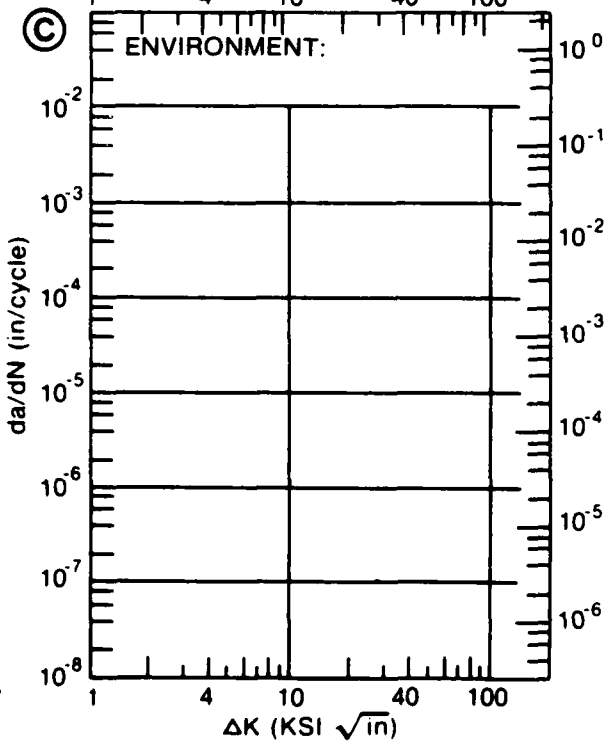
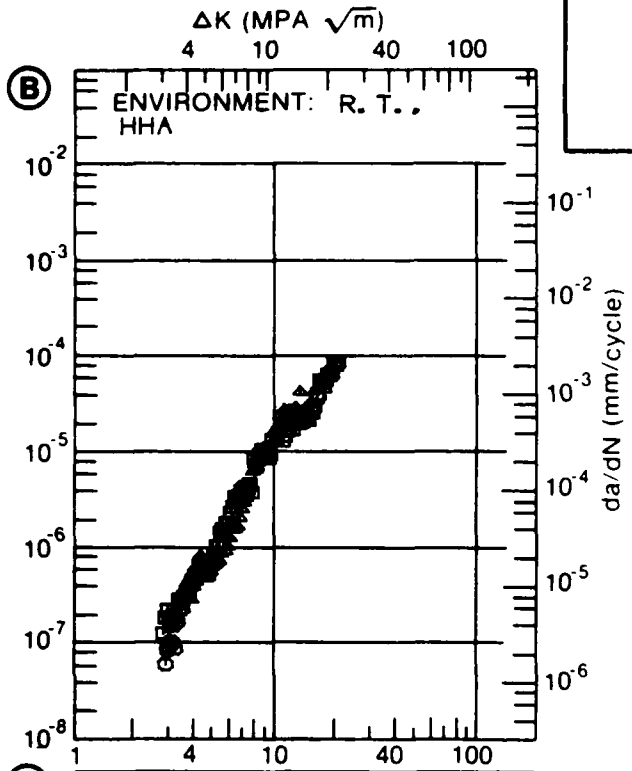
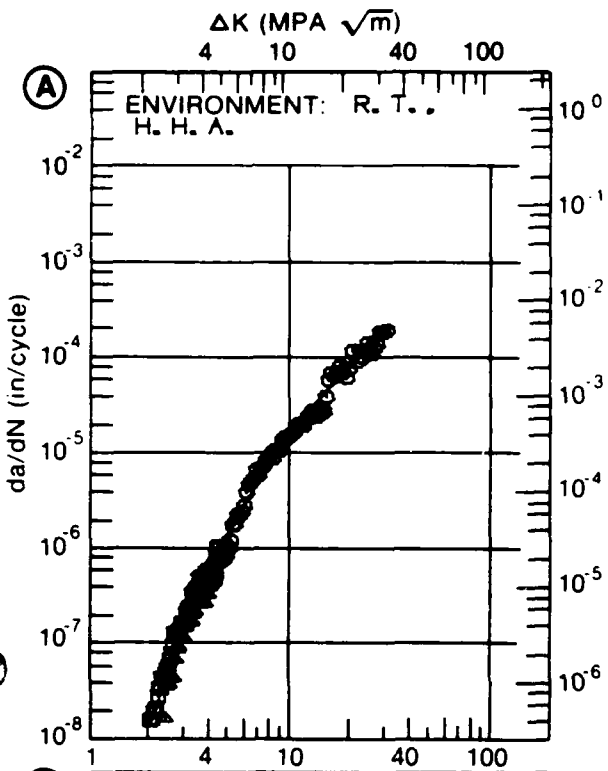


Figure 8.7.3.29

TABLE 8.7.3.30

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.30 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73651

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. 3. 5% NACL			
DELTA K MIN	A: 5.14	1.21			
	B: 6.00	2.74			
	C: 7.00	7.22			
	D: 8.00	12.2			
	9.00	16.7			
	10.00	21.6			
	13.00	50.0			
	16.00	87.0			
DELTA K MAX	A: 17.87	95.7			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 16.83
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73651
 FORM: 1.13" TH PLATE
 SPECIMEN TYPE:
 ORIENTATION:
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91332

ALUM.
ALLOY

7050

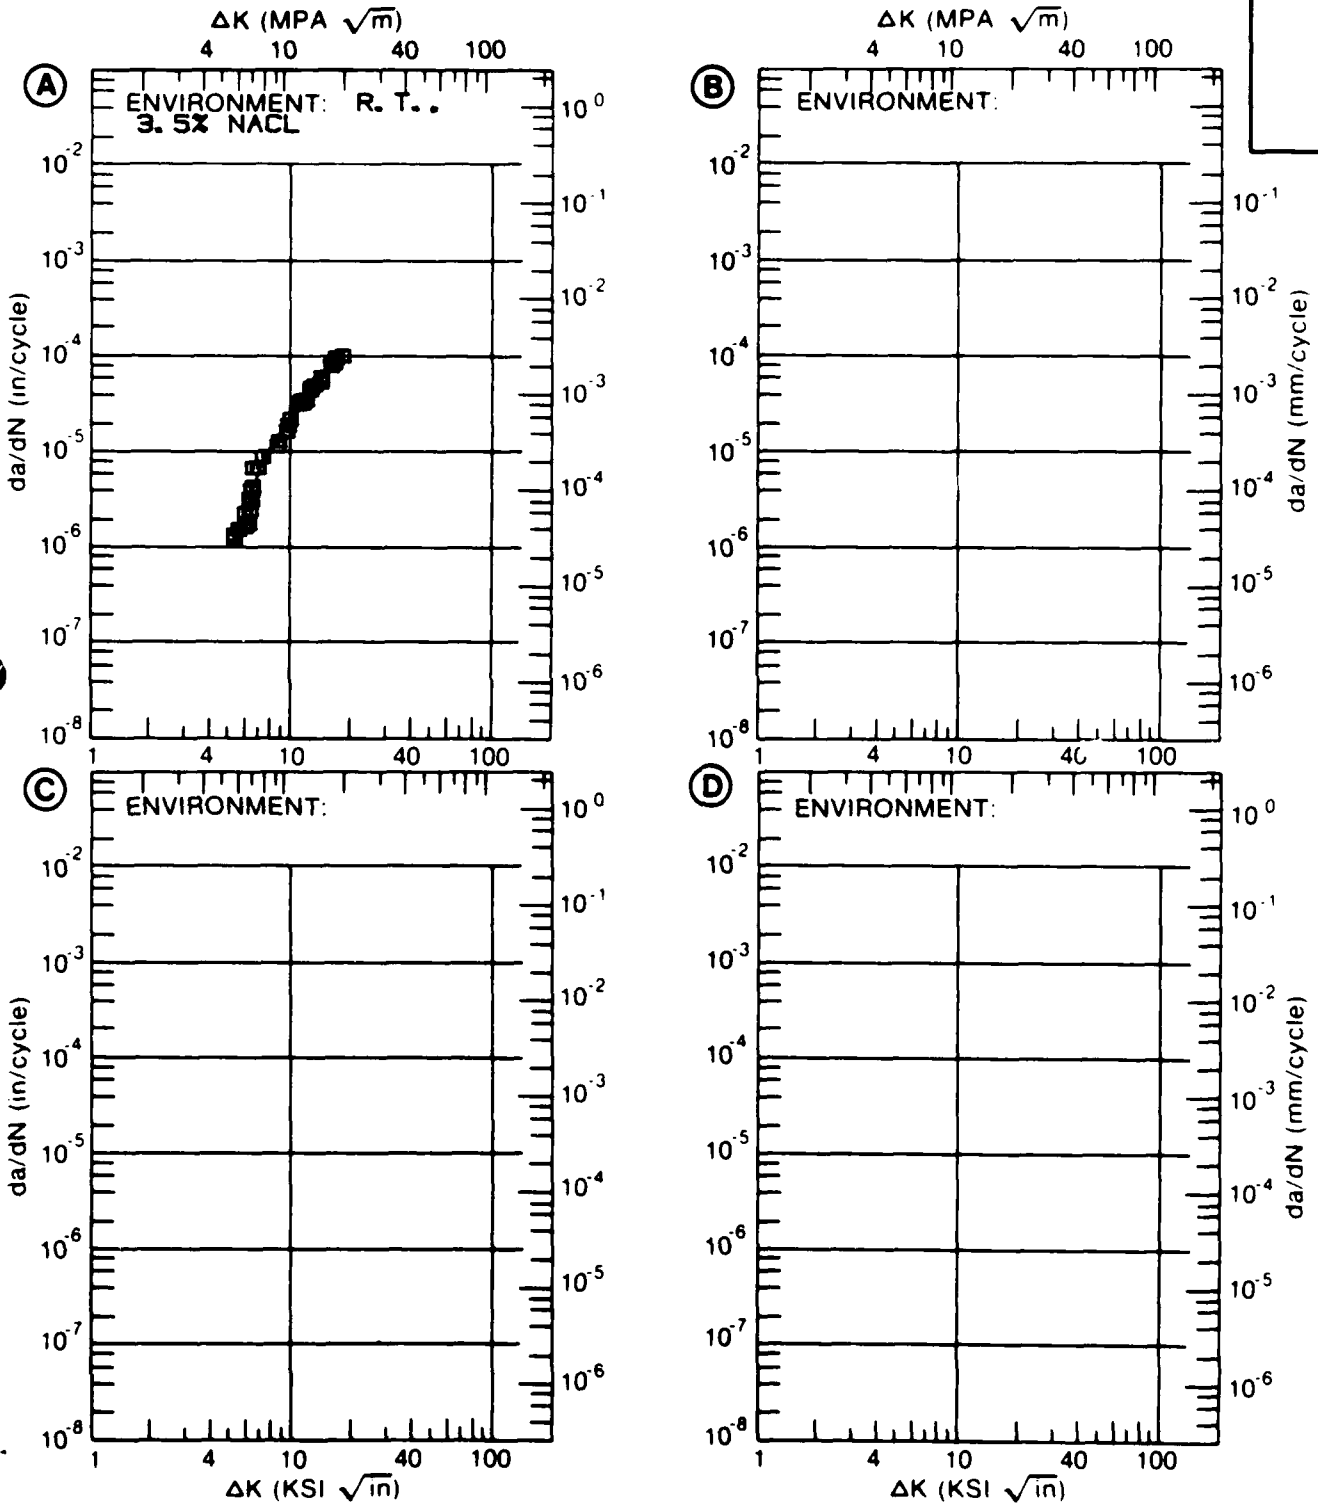


Figure 8.7.3.30

TABLE 8.7.3.31

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.31 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73651

DELTA K
(KSI*IN**1/2)

DA/DN (10**-6 IN. /CYCLE)

A

B

C

D

E: R. T.
DRY AIR

DELTA K A: 8.61 : 5.97
MIN B:
C:
D:

9.00 : 6.99
10.00 : 9.52
13.00 : 16.6
16.00 : 26.3

DELTA K A: 18.51 : 36.0
MAX B:
C:
D:

ROOT MEAN SQUARE 6.14
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73651
 FORM: 1.13" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91332

ALUM.
ALLOY

7050

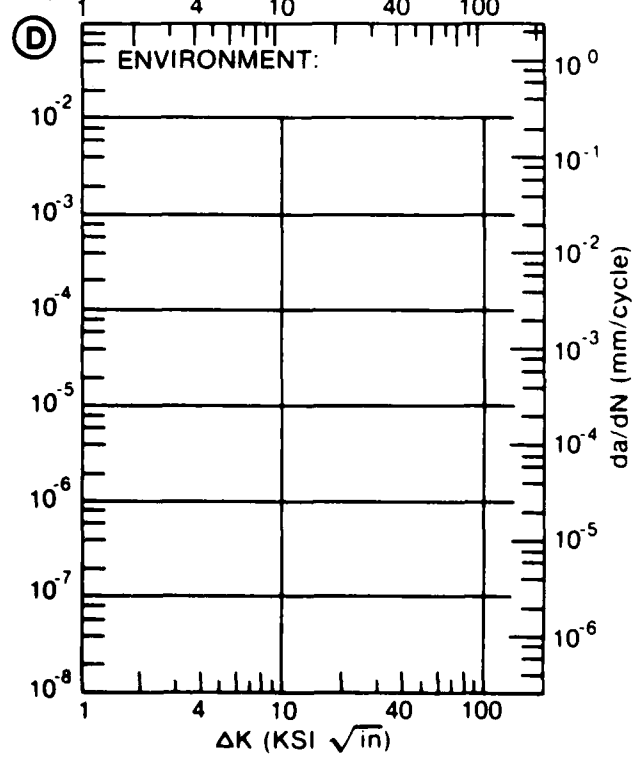
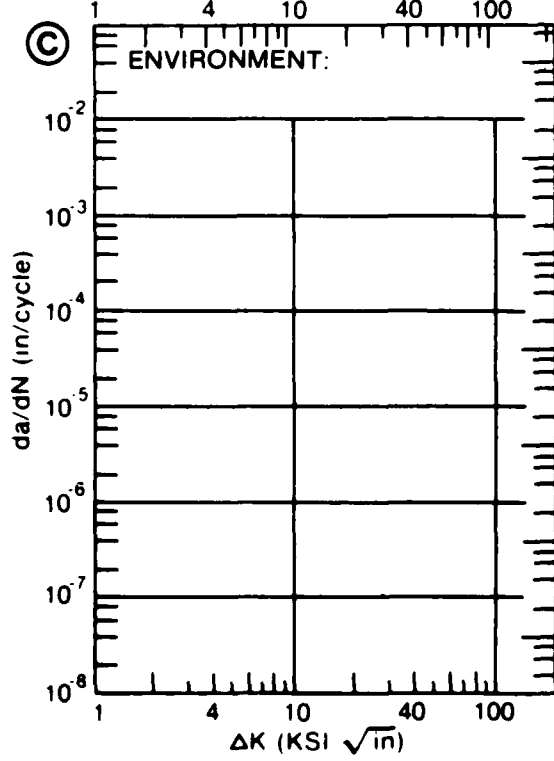
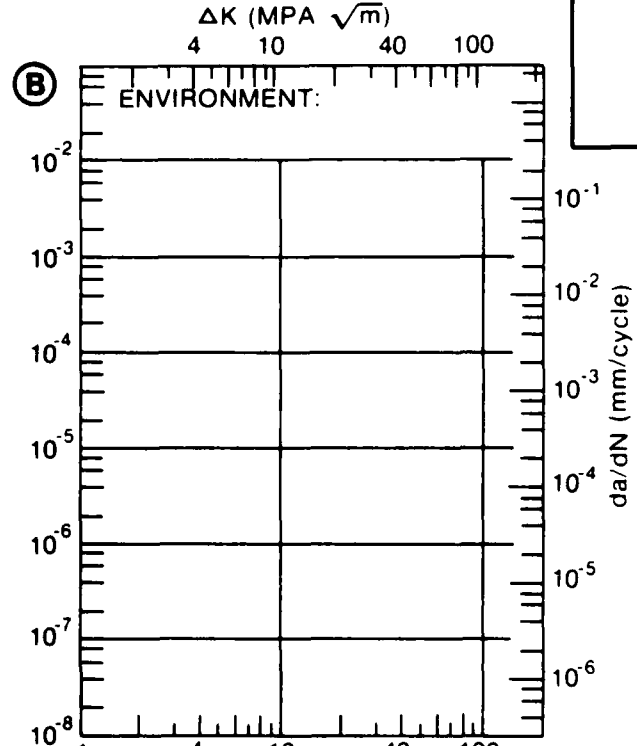
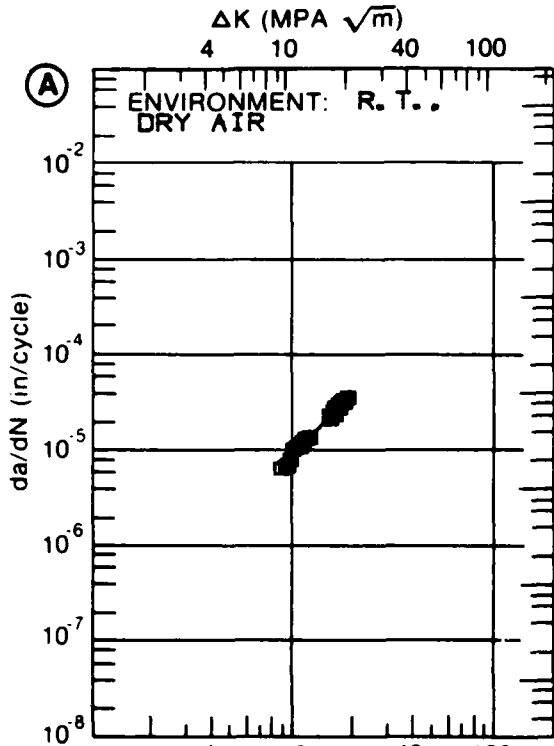


Figure 8.7.3.31

TABLE 8.7.3.32

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.32 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7050
CONDITION: T73651
ENVIRONMENT: R. T. , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.10			
DELTA K MIN	A: 7.48	3.25			
	B:				
	C:				
	D:				
	8.00	4.07			
	9.00	5.80			
	10.00	7.68			
13.00	14.3				
16.00	24.0				
20.00	47.3				
25.00	119.				
DELTA K MAX	A: 26.80	169.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 13.13
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73651
 FORM: 3.15" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 5.00- 10.00 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 65.6 KSI
 ULT. STRENGTH: 76.6 KSI
 SPECIMEN THK: 1.005"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: NC002

ALUM. ALLOY
7050

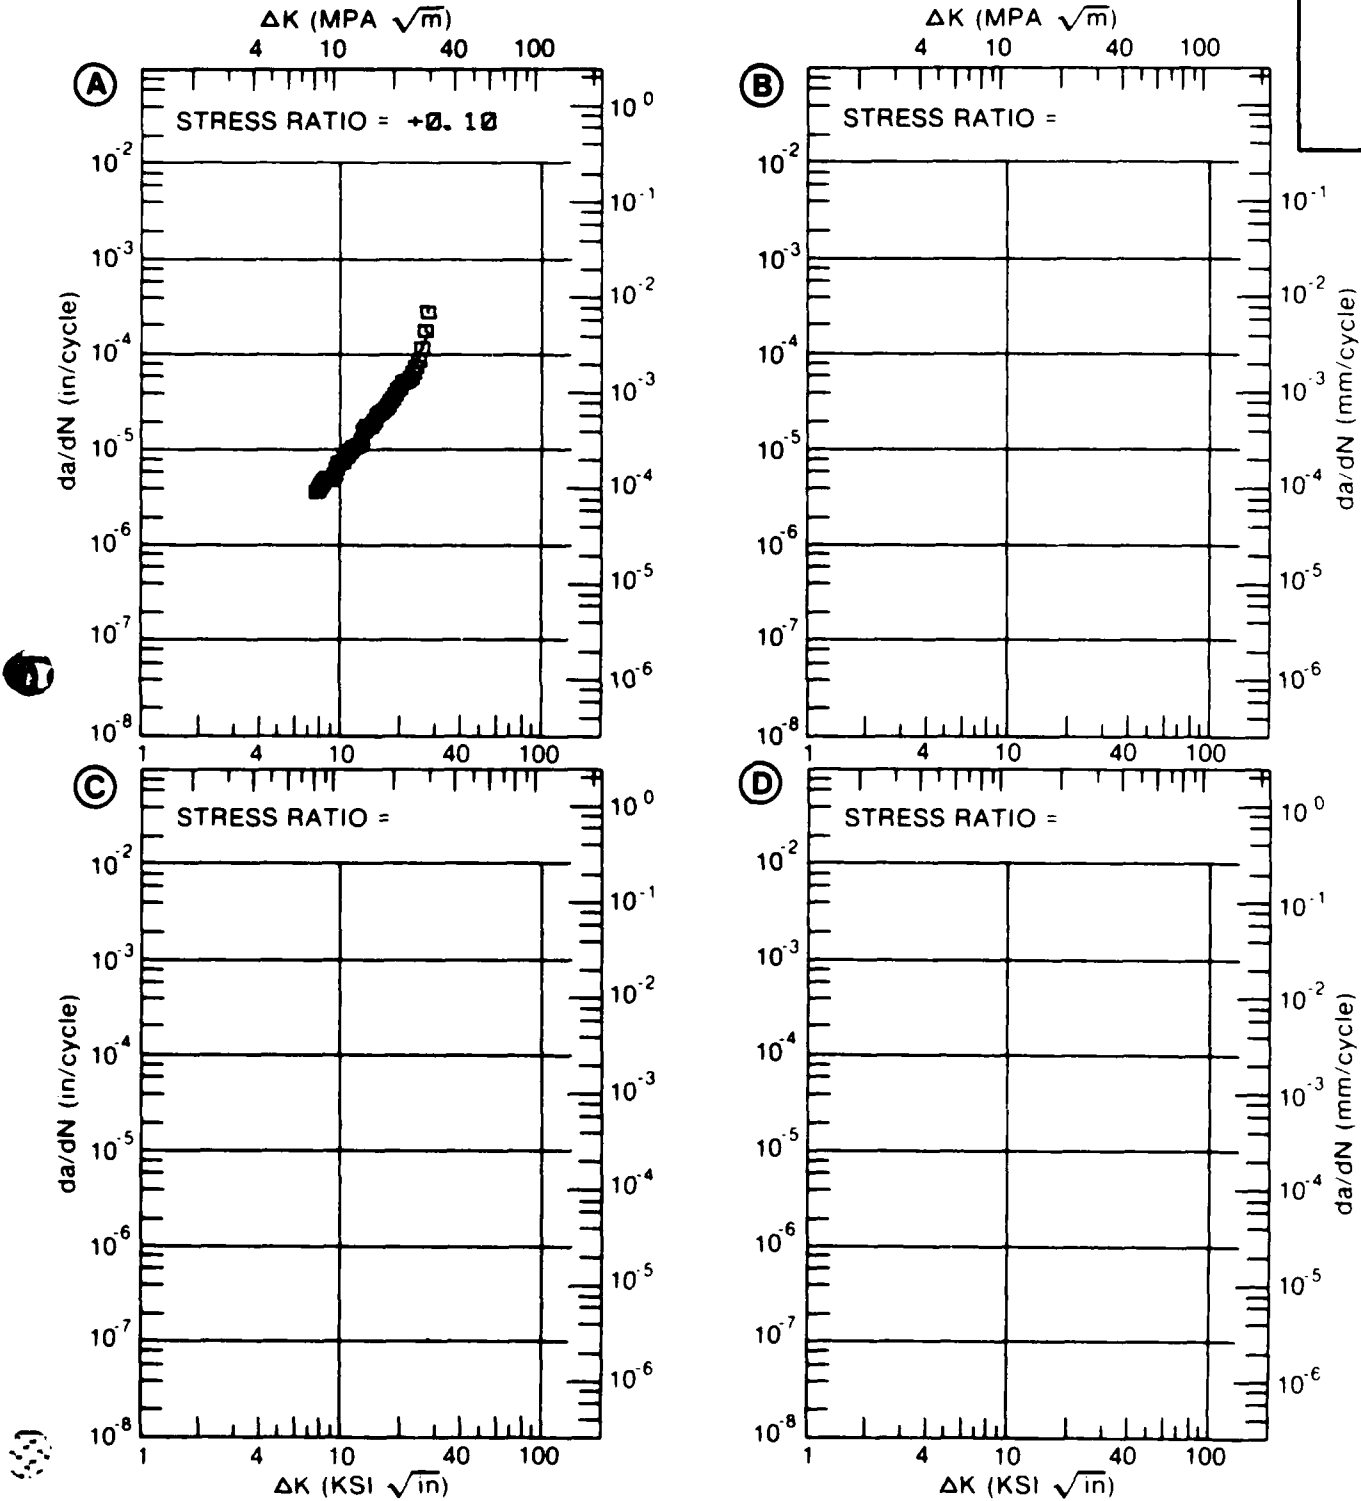


Figure 8.7.3.32

TABLE 8.7.3.33

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.33 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. SIM. SEA WATER	E= R. T. S. T. W.	
DELTA K	A: 5.86	1.01			
MIN	B: 4.80		1.70		
	C: 4.87			.993	
	D:				
	5.00		1.98	1.16	
	6.00	1.10	3.75	3.45	
	7.00	2.36	6.18	6.90	
	8.00	4.17	9.29	10.1	
	9.00	6.24	13.2	12.9	
	10.00	8.45	17.8	15.9	
	13.00	15.7	37.8	30.5	
	16.00	25.5	69.5	55.0	
	20.00	49.4	140.	97.1	
	25.00	129.	304.	195.	
	30.00	1504.			
DELTA K	A: 30.00	1504.			
MAX	B: 27.76		452.		
	C: 29.35			821.	
	D:				
ROOT MEAN SQUARE		16.60	7.81	24.18	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	2	2	3	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T73651
 FORM: 3.15" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.10
 FREQUENCY: 1.00- 10.00 HZ

YIELD STRENGTH: 69.0 KSI
 ULT. STRENGTH: 77.2 KSI
 SPECIMEN THK: 1.002- 1.005"
 SPECIMEN WIDTH: 7.400"
 REFERENCES: NC002

ALUM. ALLOY
7050

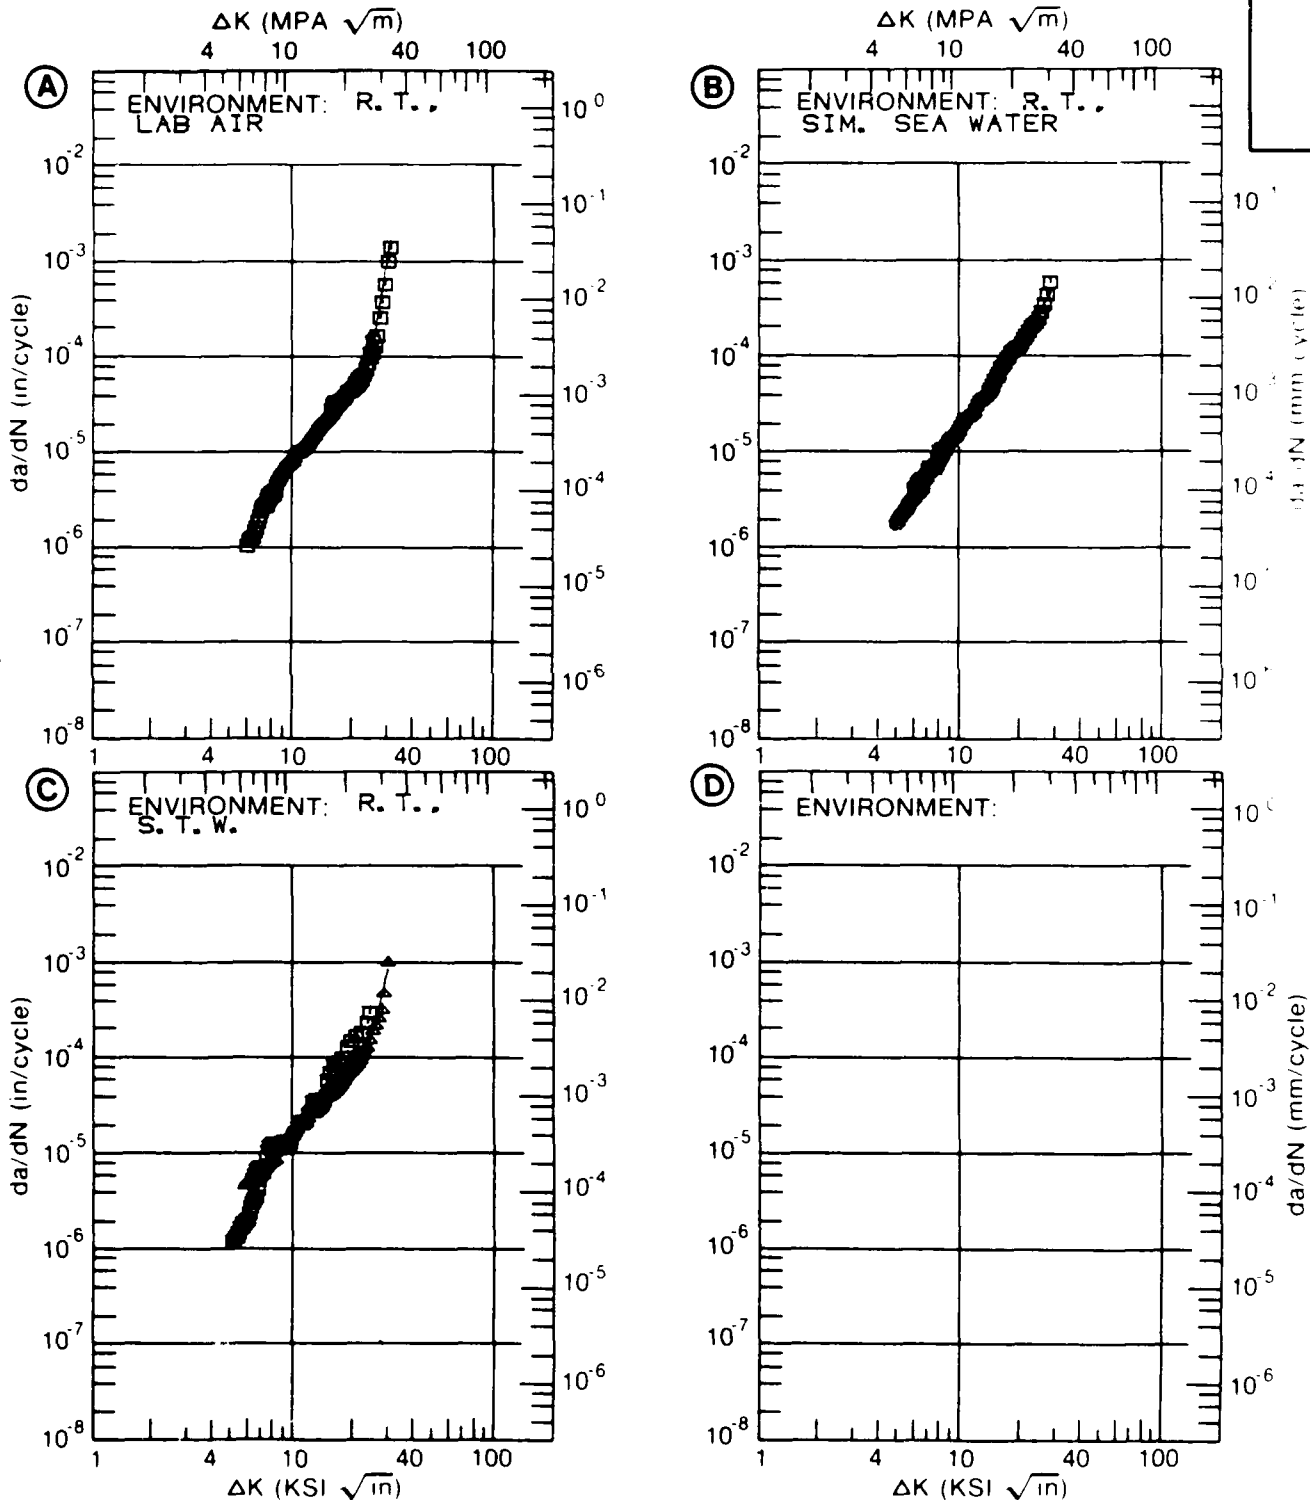


Figure 8.7.3.33

TABLE 8.7.3.34

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.34 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. LAB AIR	E= R. T. SIM. SEA WATER		
DELTA K	A: 5.68	1.22			
MIN	B: 4.47		.967		
	C:				
	D:				
	5.00		1.55		
	6.00	1.29	3.25		
	7.00	1.83	5.87		
	8.00	2.87	9.50		
	9.00	4.49	14.2		
	10.00	6.70	20.0		
	13.00	16.3	46.2		
	16.00	28.3	90.2		
	20.00	102.	191.		
DELTA K	A: 23.60	453.			
MAX	B: 21.33		238.		
	C:				
	D:				
ROOT MEAN SQUARE		15.05	25.79		
PERCENT ERROR					
LIFE PREDICTION RATIO	0.0-0.5				
	0.5-0.8				
	0.8-1.25	2	2		
SUMMARY (NP/NA)	1.25-2.0		1		
	>2.0				

CONDITION/HT: T73651
 FORM: 3.15" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-T
 STRESS RATIO: +0.10
 FREQUENCY: 1.00- 10.00 HZ

YIELD STRENGTH: 64.3 KSI
 ULT. STRENGTH: 74.5 KSI
 SPECIMEN THK: 0.499- 0.500"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: NC002

ALUM. ALLOY
7050

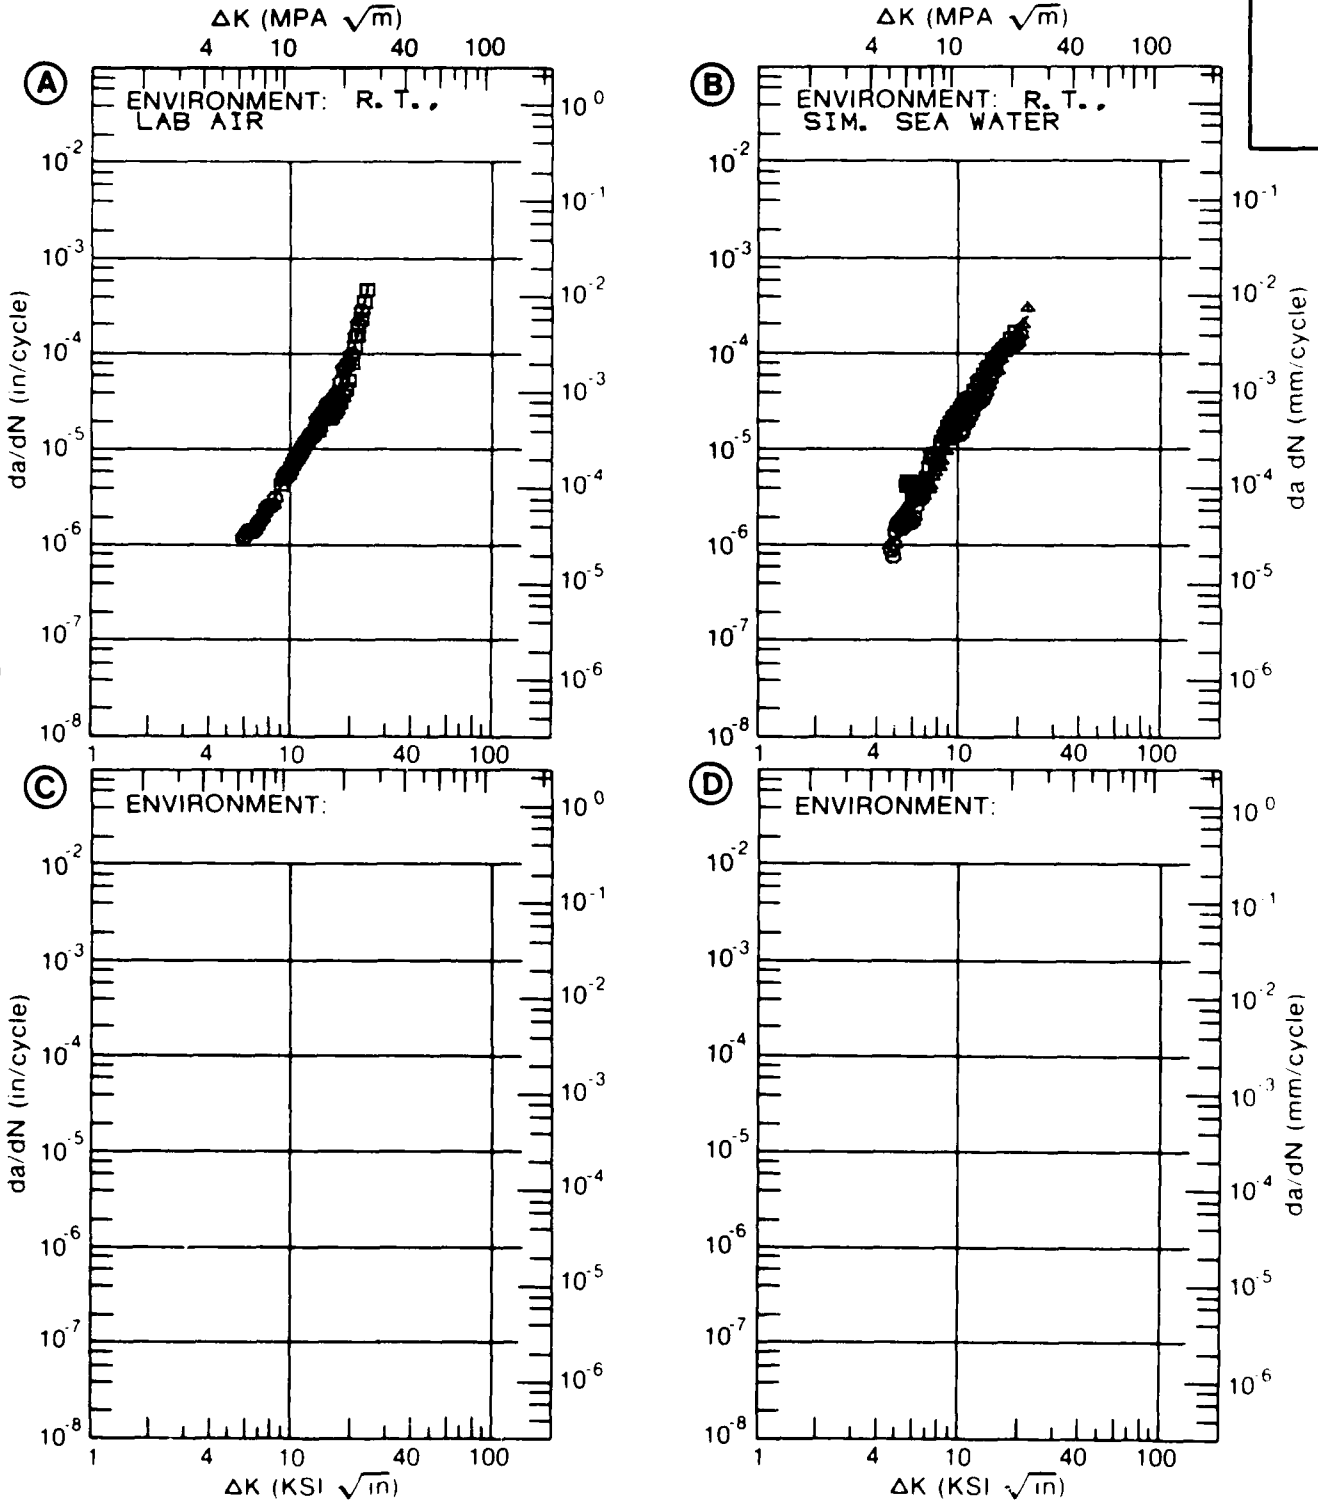


Figure 8.7.3.34

TABLE 8.7.3.35

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.35 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
ENVIRONMENT: R. T. , L. H. A.					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.08	R=+0.30	R=+0.50	
DELTA K	A: 6.89	.879			
MIN	B: 4.39		291		
	C: 5.01			.613	
	D:				
	5.00		.376		
	6.00		.628	1.34	
	7.00	.909	1.08	2.82	
	8.00	1.27	1.82	5.38	
	9.00	1.83	2.96	9.08	
	10.00	2.61	4.62	13.5	
	13.00	6.62	13.6	23.4	
	16.00	13.0	28.9		
	20.00	26.0			
DELTA K	A: 23.68	45.8			
MAX	B: 18.76		46.0		
	C: 13.34			23.6	
	D:				
ROOT MEAN SQUARE		11.09	18.90	11.72	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1		1	
SUMMARY	1.25-2.0		1		
(NP/NA)	>2.0				

CONDITION/HT: T73651
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 6.00 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 65.0 KSI
 ULT. STRENGTH: 80.0 KSI
 SPECIMEN THK: 0.992- 0.993"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837

ALUM. ALLOY
7050

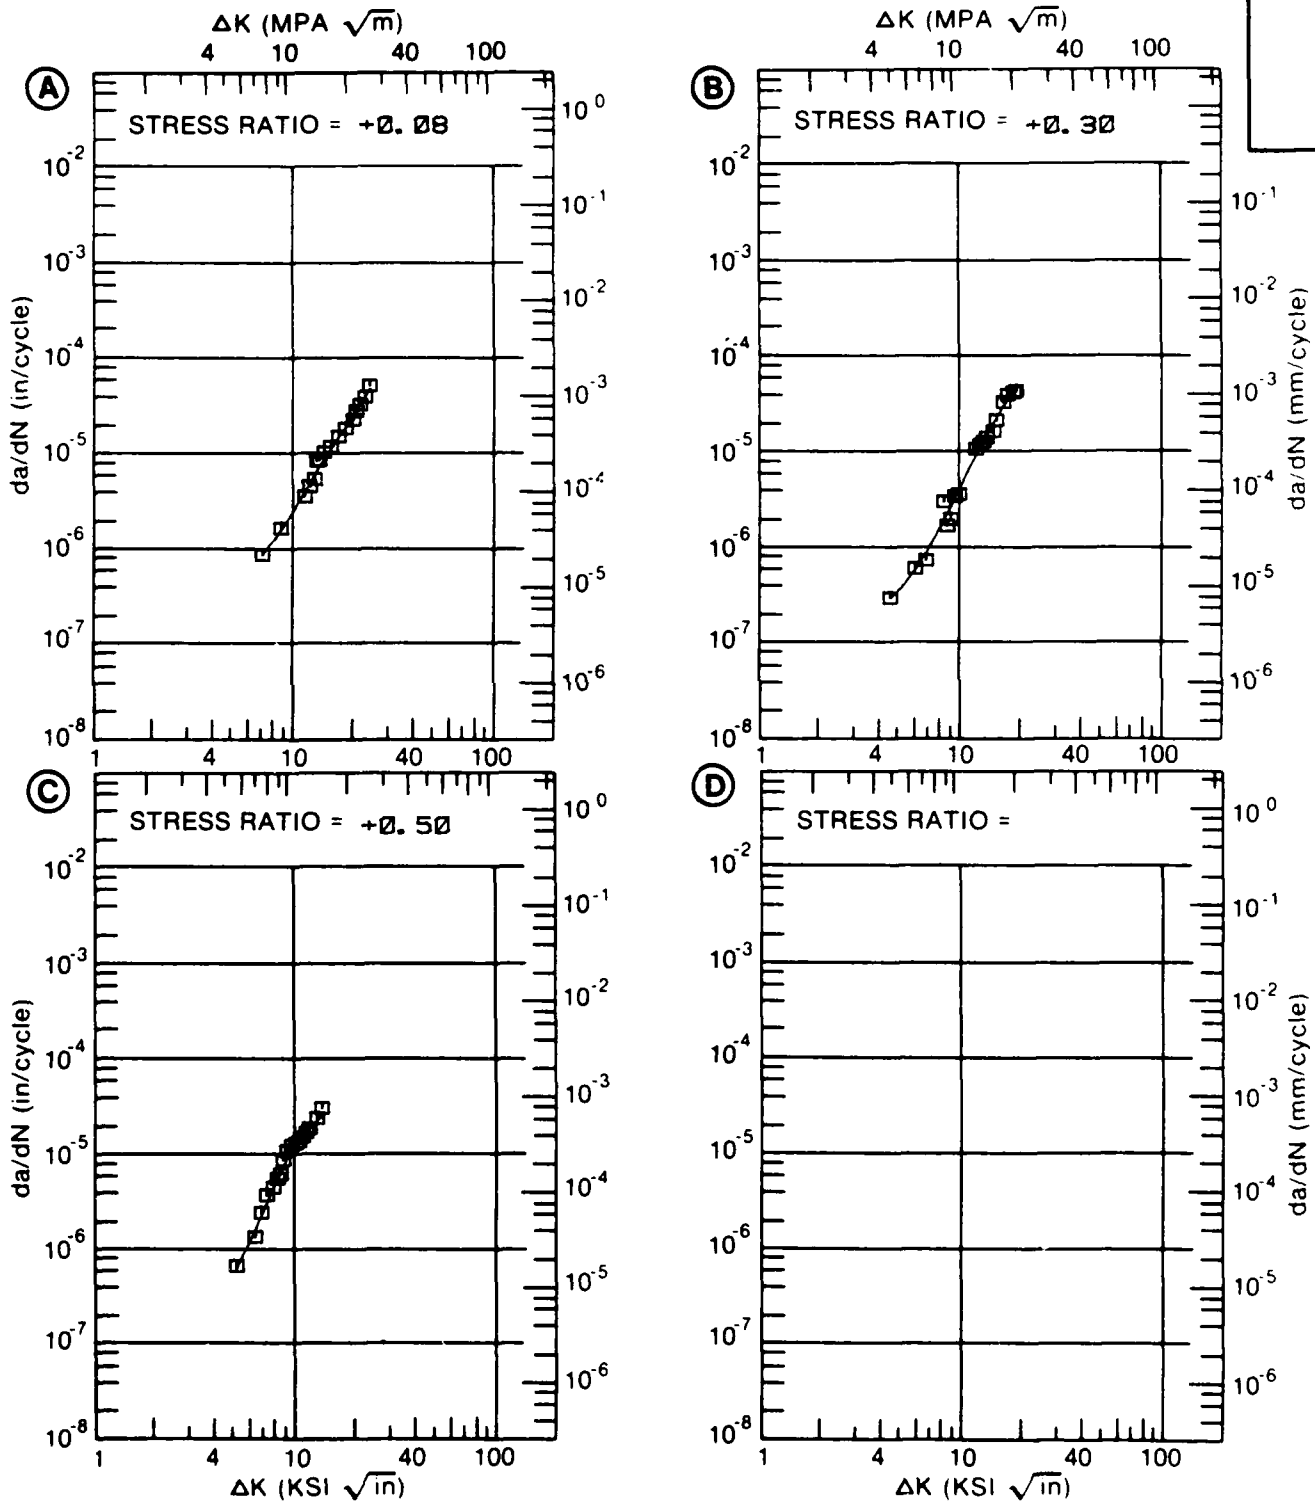


Figure 8.7.3.35

TABLE 8.7.3.36

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.36 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T73651

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN. /CYCLE)			
	A	B	C	D
	E= R. T. L. H. A 6HZ	E= R. T. S. T. W 1HZ		
DELTA K MIN	A: 4.75	.20	B: 1.92	
	B: 7.08			
	C:			
	D:			
	5.00	.242		
	6.00	.446		
	7.00	.766		
	8.00	1.24	5.07	
	9.00	1.92	9.34	
	10.00	2.87	13.3	
	13.00	8.02	23.9	
	16.00	18.6	49.6	
DELTA K MAX	A: 18.39	33.2	B: 62.9	
	B: 16.70			
	C:			
	D:			

ROOT MEAN SQUARE 11.45 15.46
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0 1
(NP/NA) 2.0

CONDITION/HT: T73651
 FORM: 4.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.08
 FREQUENCY:

YIELD STRENGTH: 65.0- 86.0 KSI
 ULT. STRENGTH: 76.0- 80.0 KSI
 SPECIMEN THK: 0.990- 0.993"
 SPECIMEN WIDTH: 6.000"
 REFERENCES: 85837, 88579

ALUM. ALLOY
7050

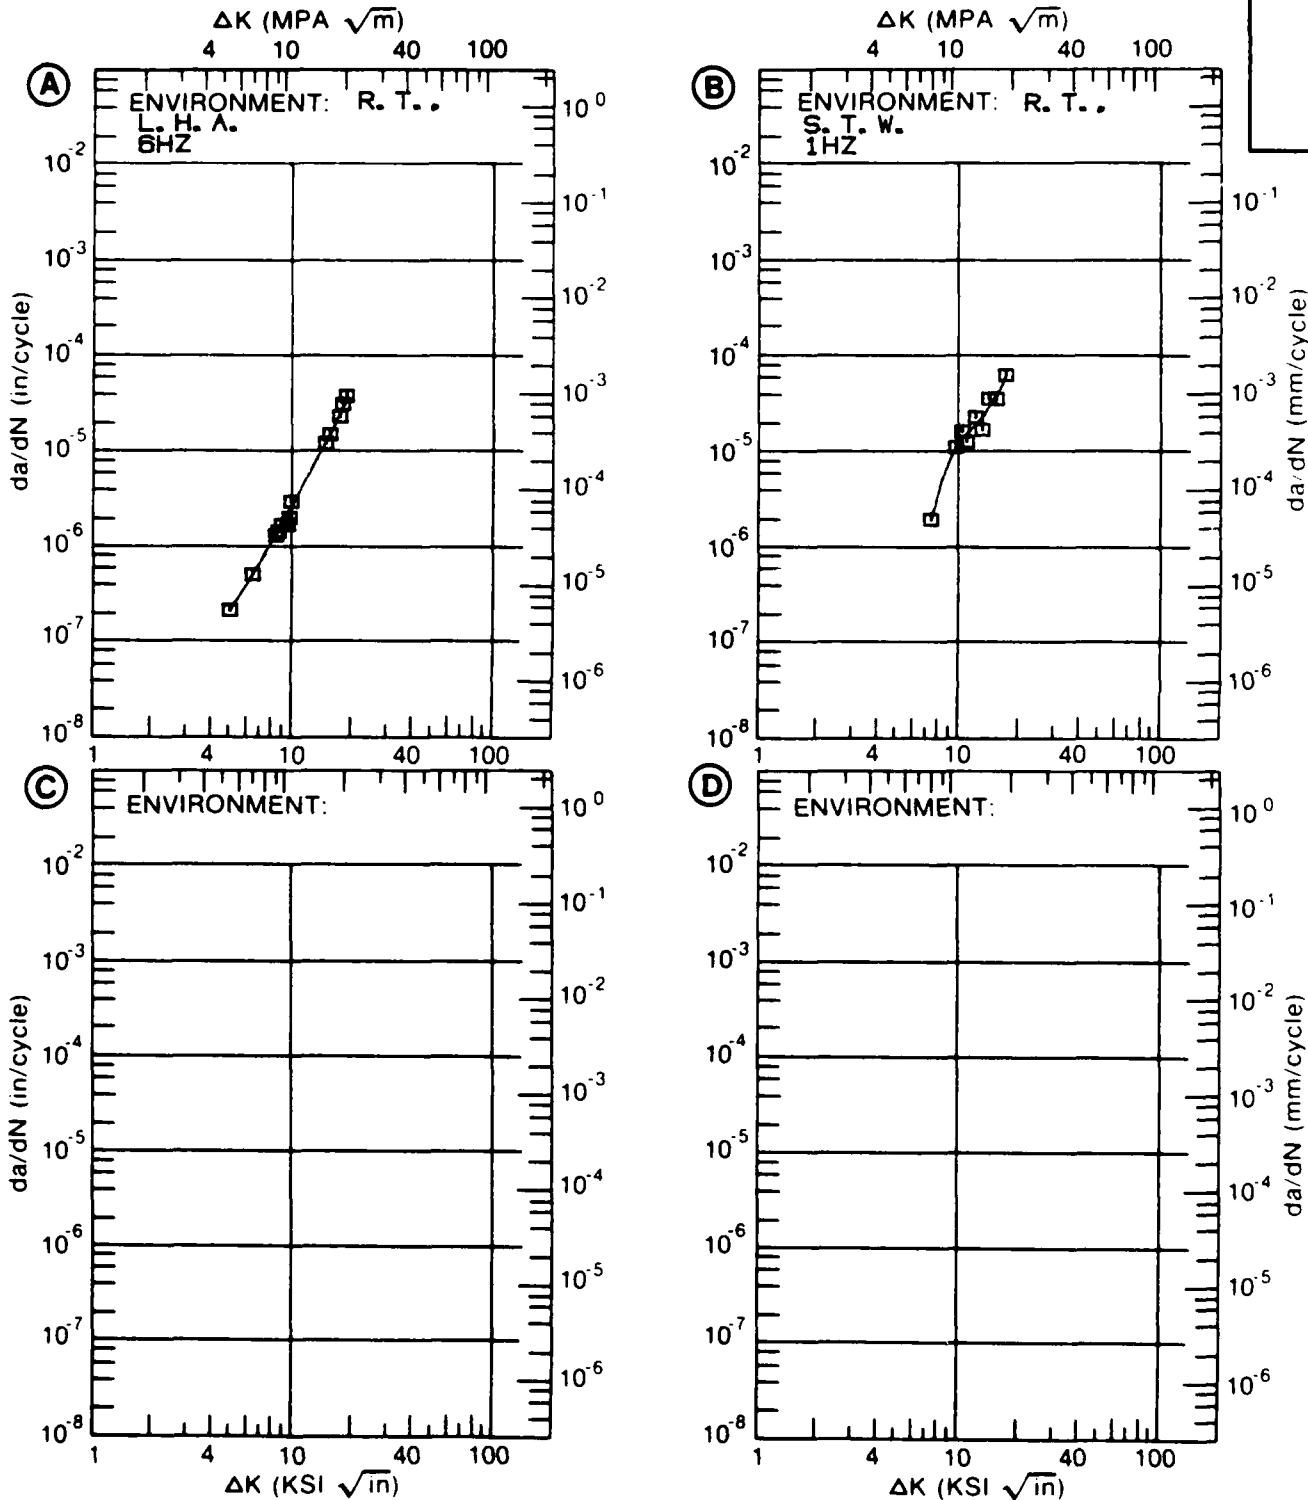


Figure 8.7.3.36

TABLE 8.7.3.37

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.37 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K	A: 5.79	1.05			
MIN	B: 5.80		1.79		
	C: 8.11			13.9	
	D:				
	6.00	1.14	2.17		
	7.00	2.23	4.43		
	8.00	4.15	7.03		
	9.00	6.67	9.76	14.9	
	10.00	9.39	12.7	20.8	
	13.00	16.2	24.7	31.0	
	16.00	28.5	52.2	54.0	
DELTA K	A: 18.46	59.6			
MAX	B: 17.57		82.1		
	C: 17.24			74.3	
	D:				
ROOT MEAN SQUARE		7.17	5.54	9.79	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T73651
 FORM: 6.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 60.9 KSI
 ULT. STRENGTH: 69.7 KSI
 SPECIMEN THK: 0.998- 1.000"
 SPECIMEN WIDTH: 3.801- 3.805"
 REFERENCES: AL013

ALUM.
ALLOY

7050

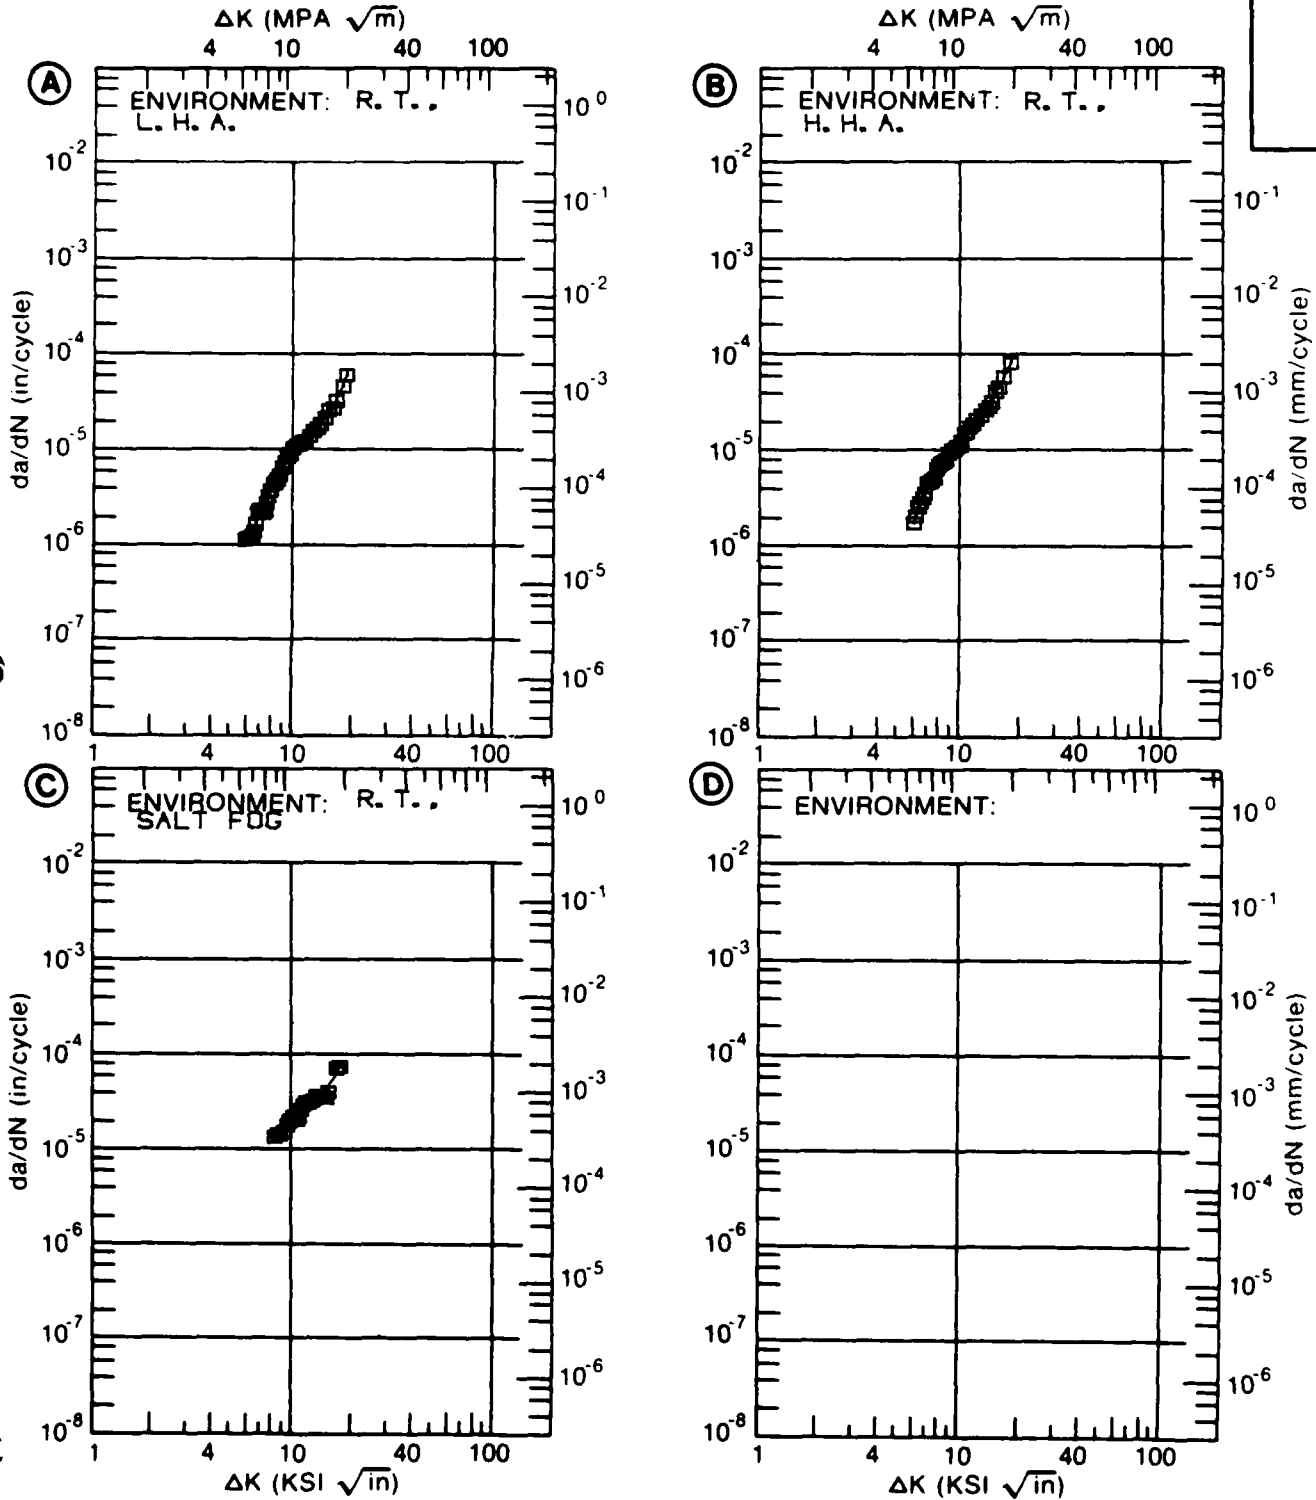


Figure 8.7.3.37

TABLE 8.7.3.38

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.38 INDICATING EFFECT

OF STRESS RATIO

MATERIAL: ALUMINUM 7050
CONDITION: T73651
ENVIRONMENT: R.T., SALT FOG

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		R=+0.03			
DELTA K MIN	A: 8.45	6.11			
	B:				
	C:				
	D:				
	9.00	8.55			
	10.00	13.1			
	13.00	25.3			
	16.00	43.0			
DELTA K MAX	A: 19.57	112.			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 7.13
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T73651
 FORM: 6.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 18.30 HZ
 ENVIRONMENT: R. T., SALT FOG

YIELD STRENGTH: 59.1 KSI
 ULT. STRENGTH: 70.5 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.801"
 REFERENCES: AL013

ALUM.
 ALLOY
 7050

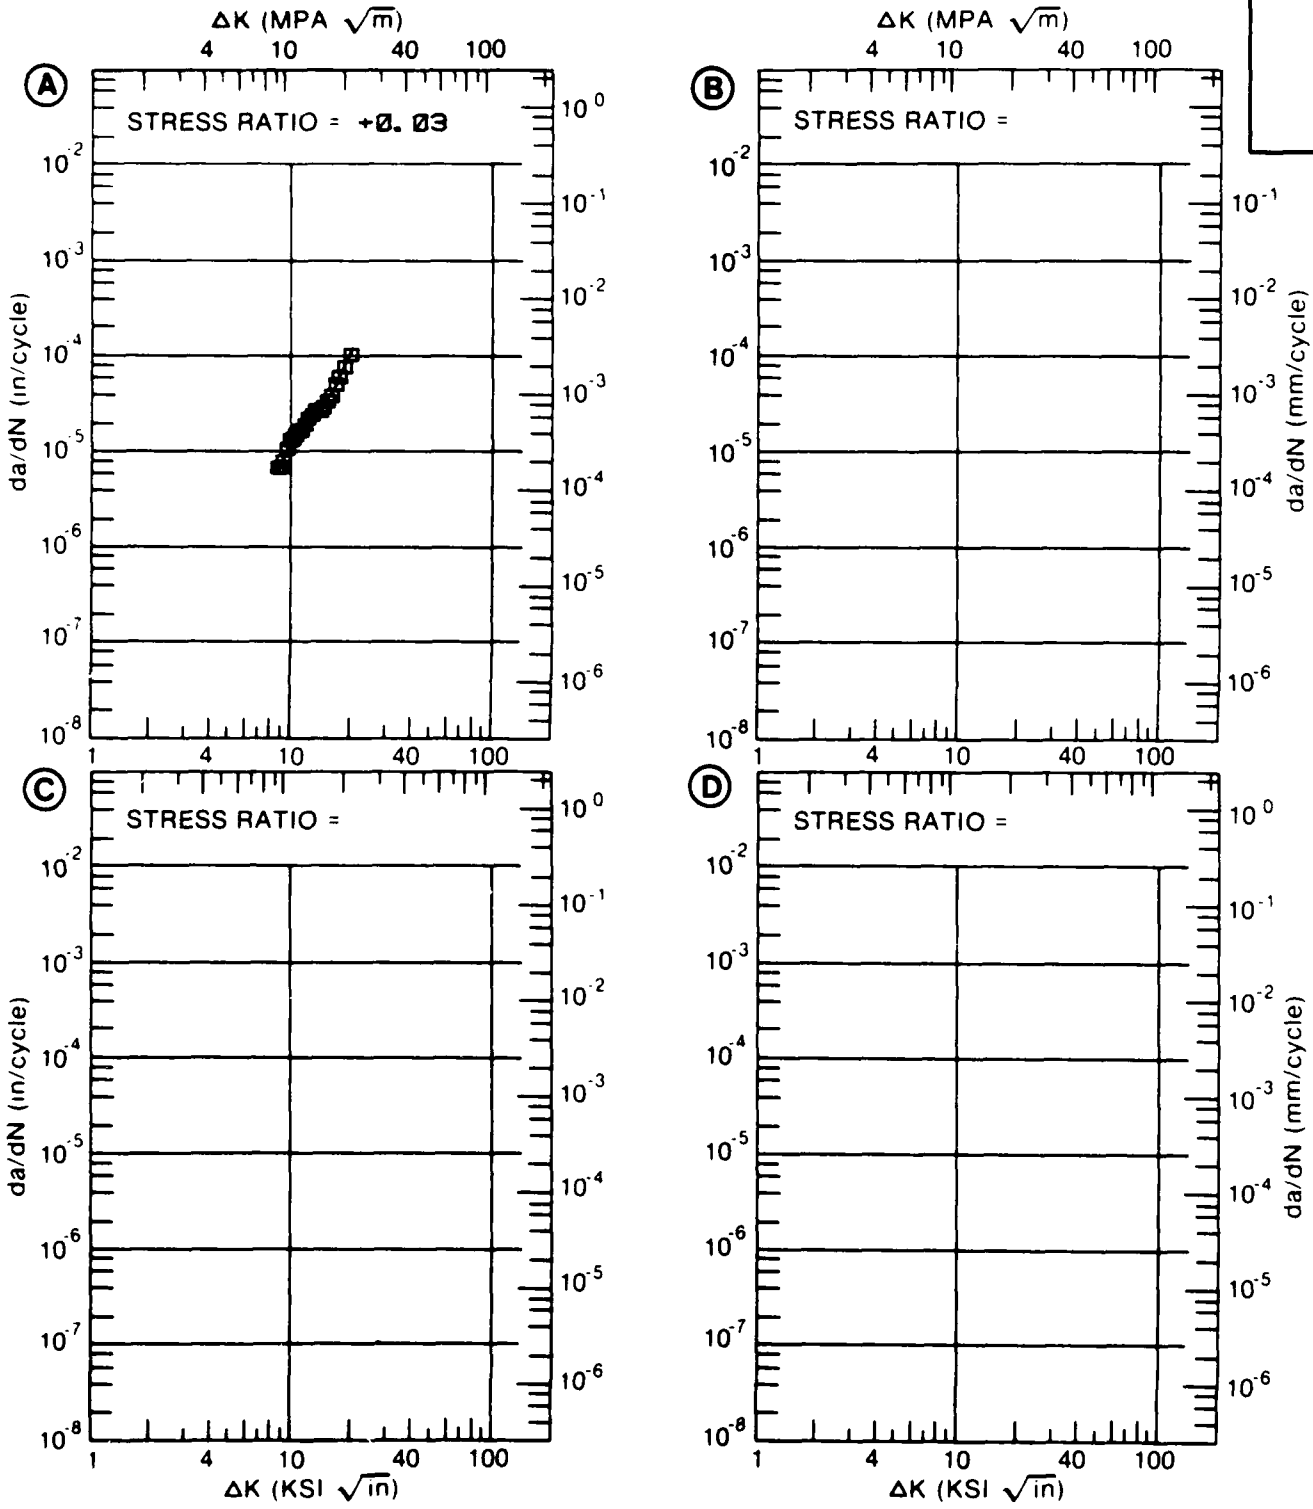


Figure 8.7.3.38

TABLE 8.7.3.39

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.39 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K	A: 3.91	.288			
MIN	B: 3.88		.510		
	C: 5.91			3.88	
	D:				
	4.00	.296	.495		
	5.00	.520	.944		
	6.00	1.06	2.39	4.25	
	7.00	2.04	4.58	8.45	
	8.00	3.38	7.39	12.0	
	9.00	4.87	10.9	15.0	
	10.00	6.75	15.5	18.4	
	13.00	26.8	41.1	44.4	
DELTA K	A: 15.34	106.			
MAX	B: 14.54		112.		
	C: 13.62			57.8	
	D:				
ROOT MEAN SQUARE		19.68	12.17	10.16	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	3	2	2	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T73651
 FORM: 8.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 59.1- 62.1 KSI
 ULT. STRENGTH: 70.5- 73.2 KSI
 SPECIMEN THK: 0.999- 1.000"
 SPECIMEN WIDTH: 3.801- 3.805"
 REFERENCES: AL013

ALUM. ALLOY
7050

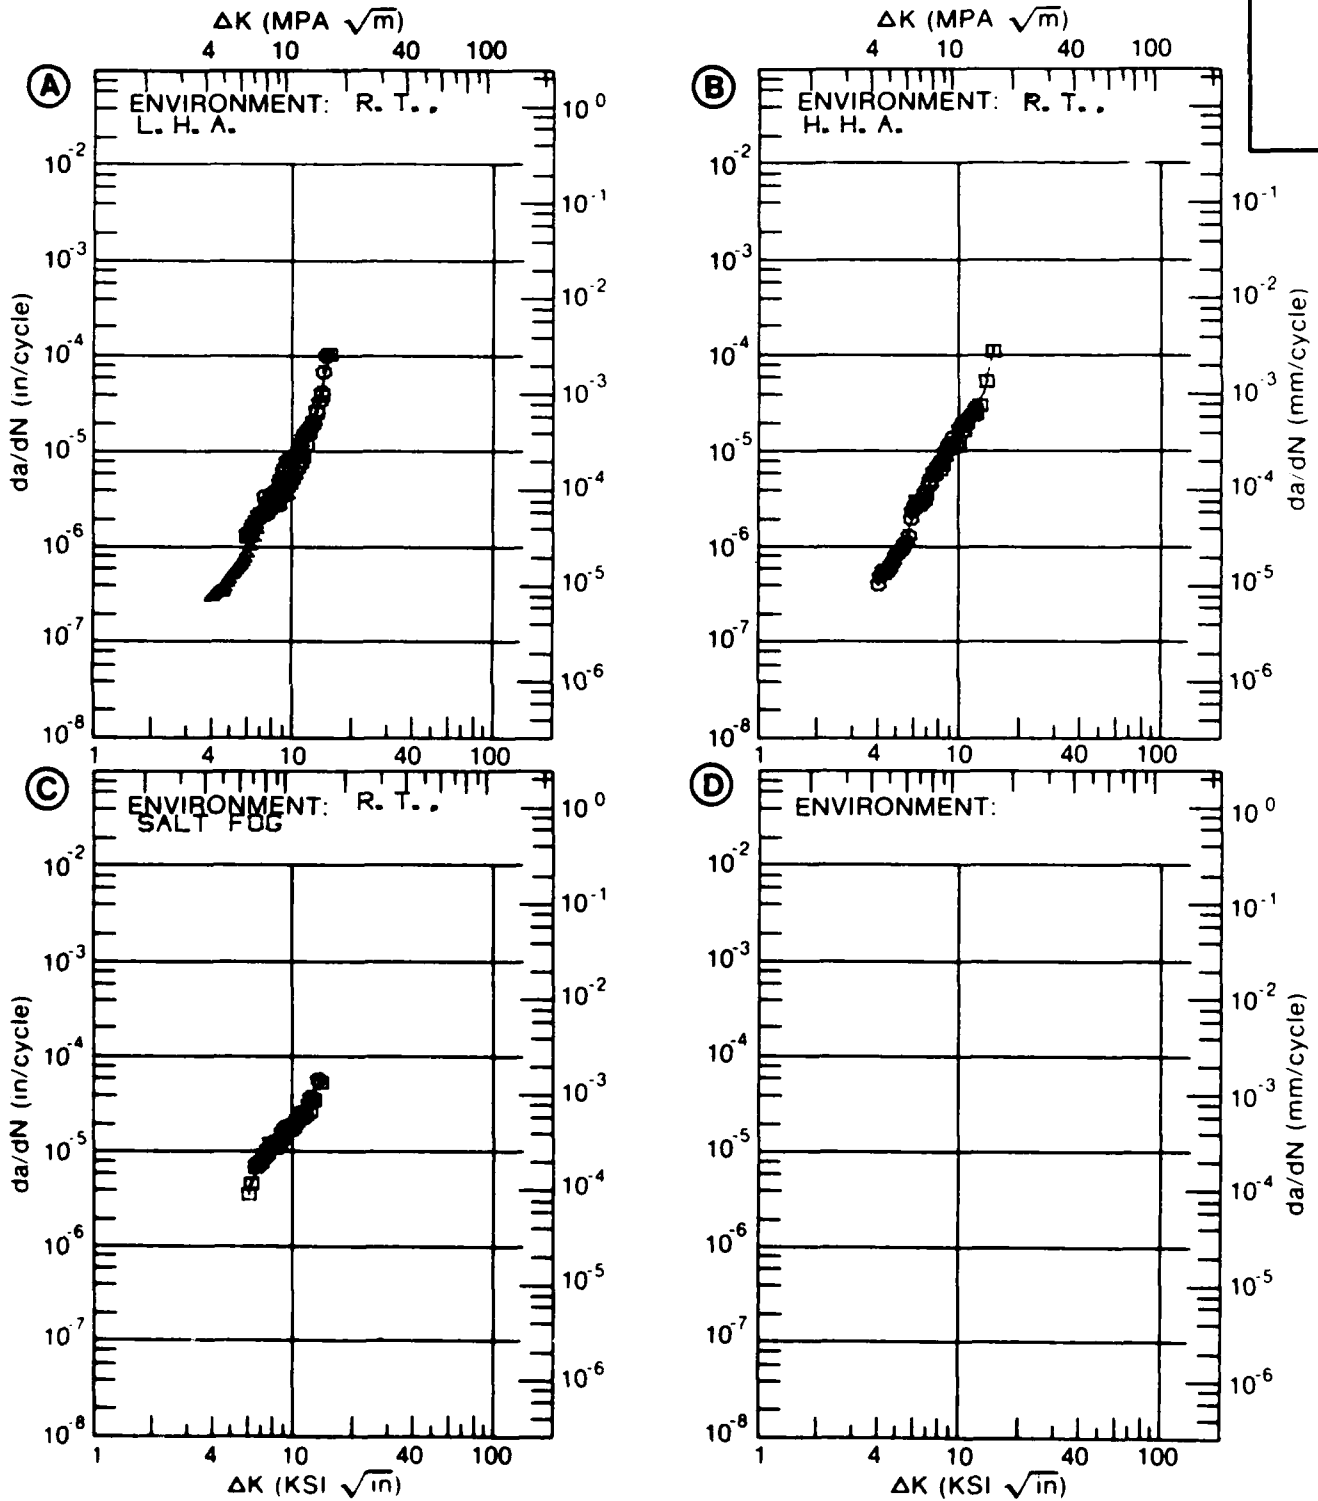


Figure 8.7.3.39

TABLE 8.7.3.40

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.40 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.82	1.46			
	B: 5.86		2.69		
	C: 5.89			6.56	
	D:				
	6.00	1.57	2.60	6.65	
	7.00	2.15	4.43	8.01	
	8.00	2.79	7.59	10.3	
	9.00	3.72	11.0	13.7	
	10.00	5.27	14.9	18.5	
	13.00	23.6	38.3	46.0	
DELTA K MAX	A: 15.19	105.			
	B: 14.64		74.1		
	C: 13.28			49.9	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		13.56	9.03	9.23	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1	

CONDITION/HT: T73651
 FORM: 6.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 56.8 KSI
 ULT. STRENGTH: 67.7 KSI
 SPECIMEN THK: 0.998- 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL013

ALUM. ALLOY
7050

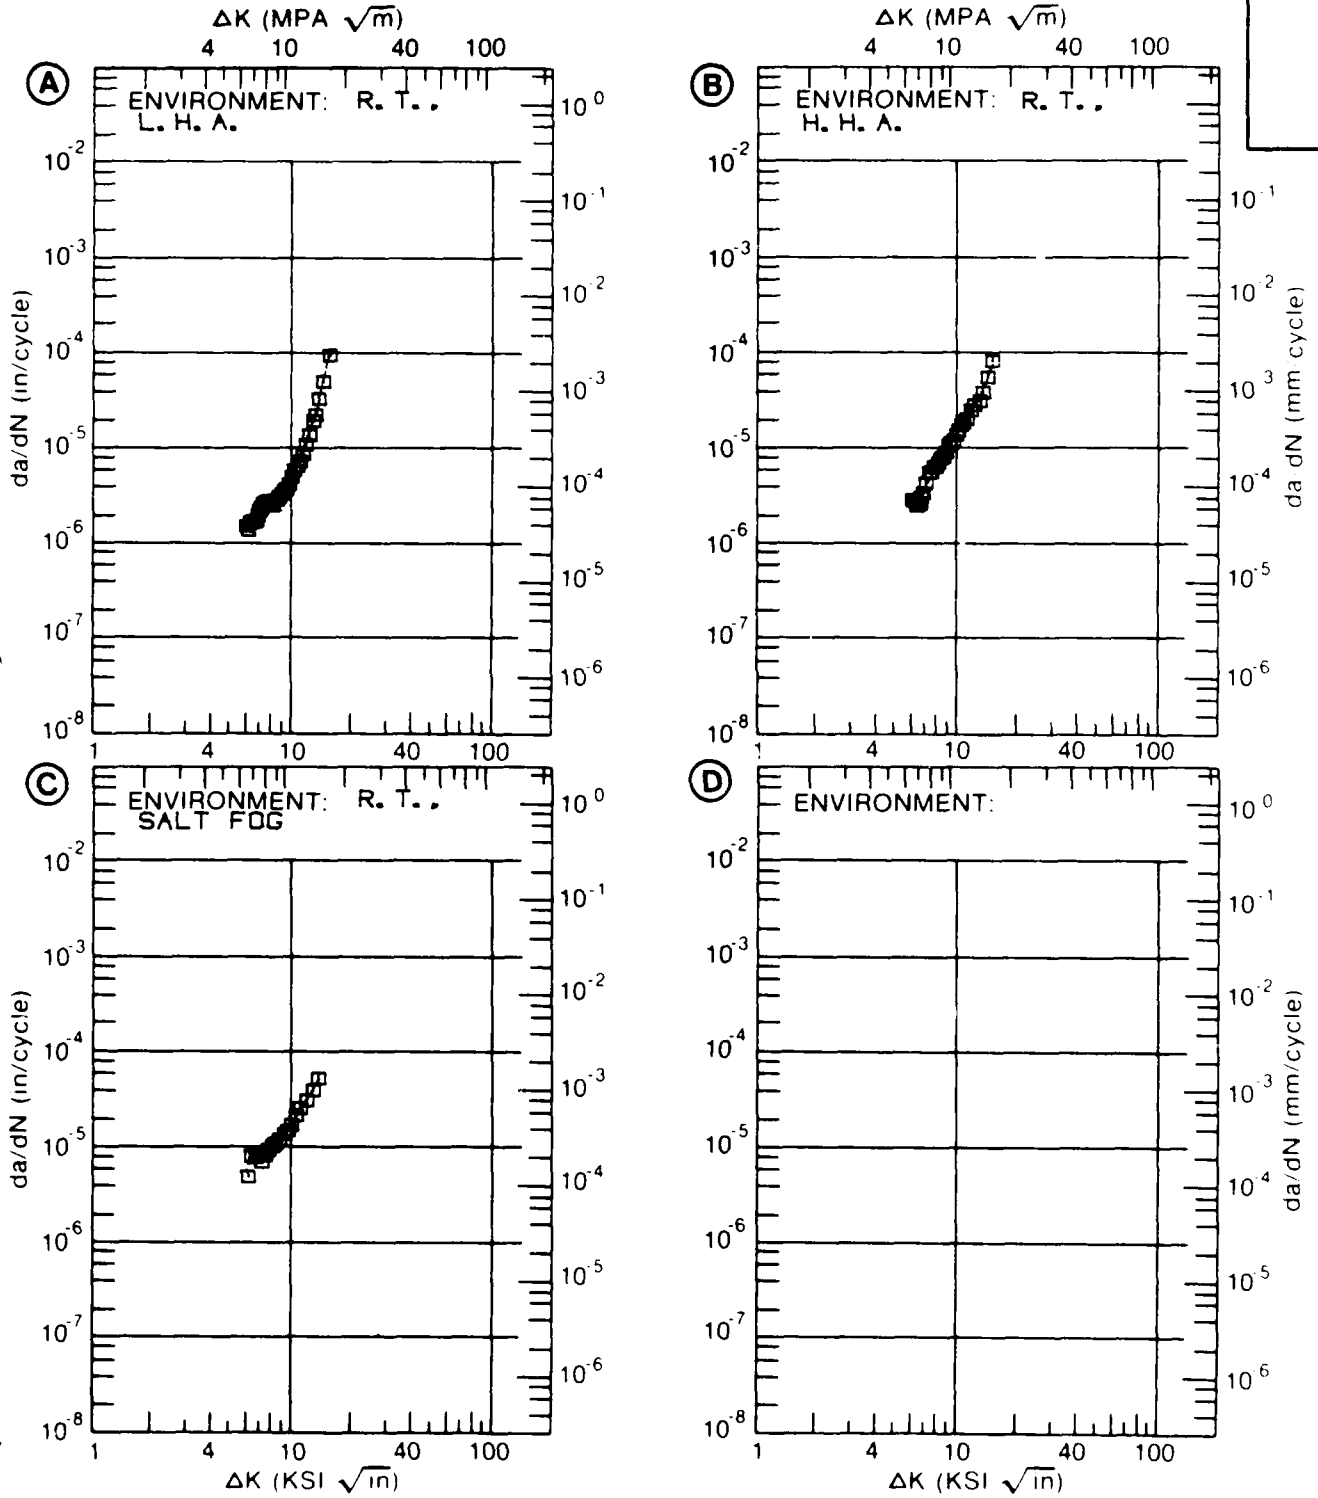


Figure 8.7.3.40

TABLE 8.7.3.41

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.41 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73651					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. H. H. A. 2HZ	E= R. T. 3. 5% NACL 20HZ		
DELTA K	A: 2.88	.053			
MIN	B: 7.42		2.36		
	C:				
	D:				
	3.00	.0607			
	3.50	.0983			
	4.00	.152			
	5.00	.330			
	6.00	.662			
	7.00	1.25			
	8.00	2.23	3.17		
	9.00	3.72	4.90		
	10.00	5.81	7.01		
	13.00	15.6	15.5		
	16.00	28.6	26.9		
	20.00	49.0	46.4		
	25.00	82.6			
	30.00	135.			
	35.00	223.			
	40.00	380.			
DELTA K	A: 45.76	726.			
MAX	B: 20.84		51.1		
	C:				
	D:				
ROOT MEAN SQUARE		22.51	8.95		
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25		1		
SUMMARY	1.25-2.0	1			
(NP/NA)	>2.0				

CONDITION/HT: T73651
 FORM: Ø. 44- 1.00" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +Ø. 1Ø
 FREQUENCY:

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: Ø. 151"
 SPECIMEN WIDTH: 3.000"
 REFERENCES:86844

ALUM. ALLOY
7050

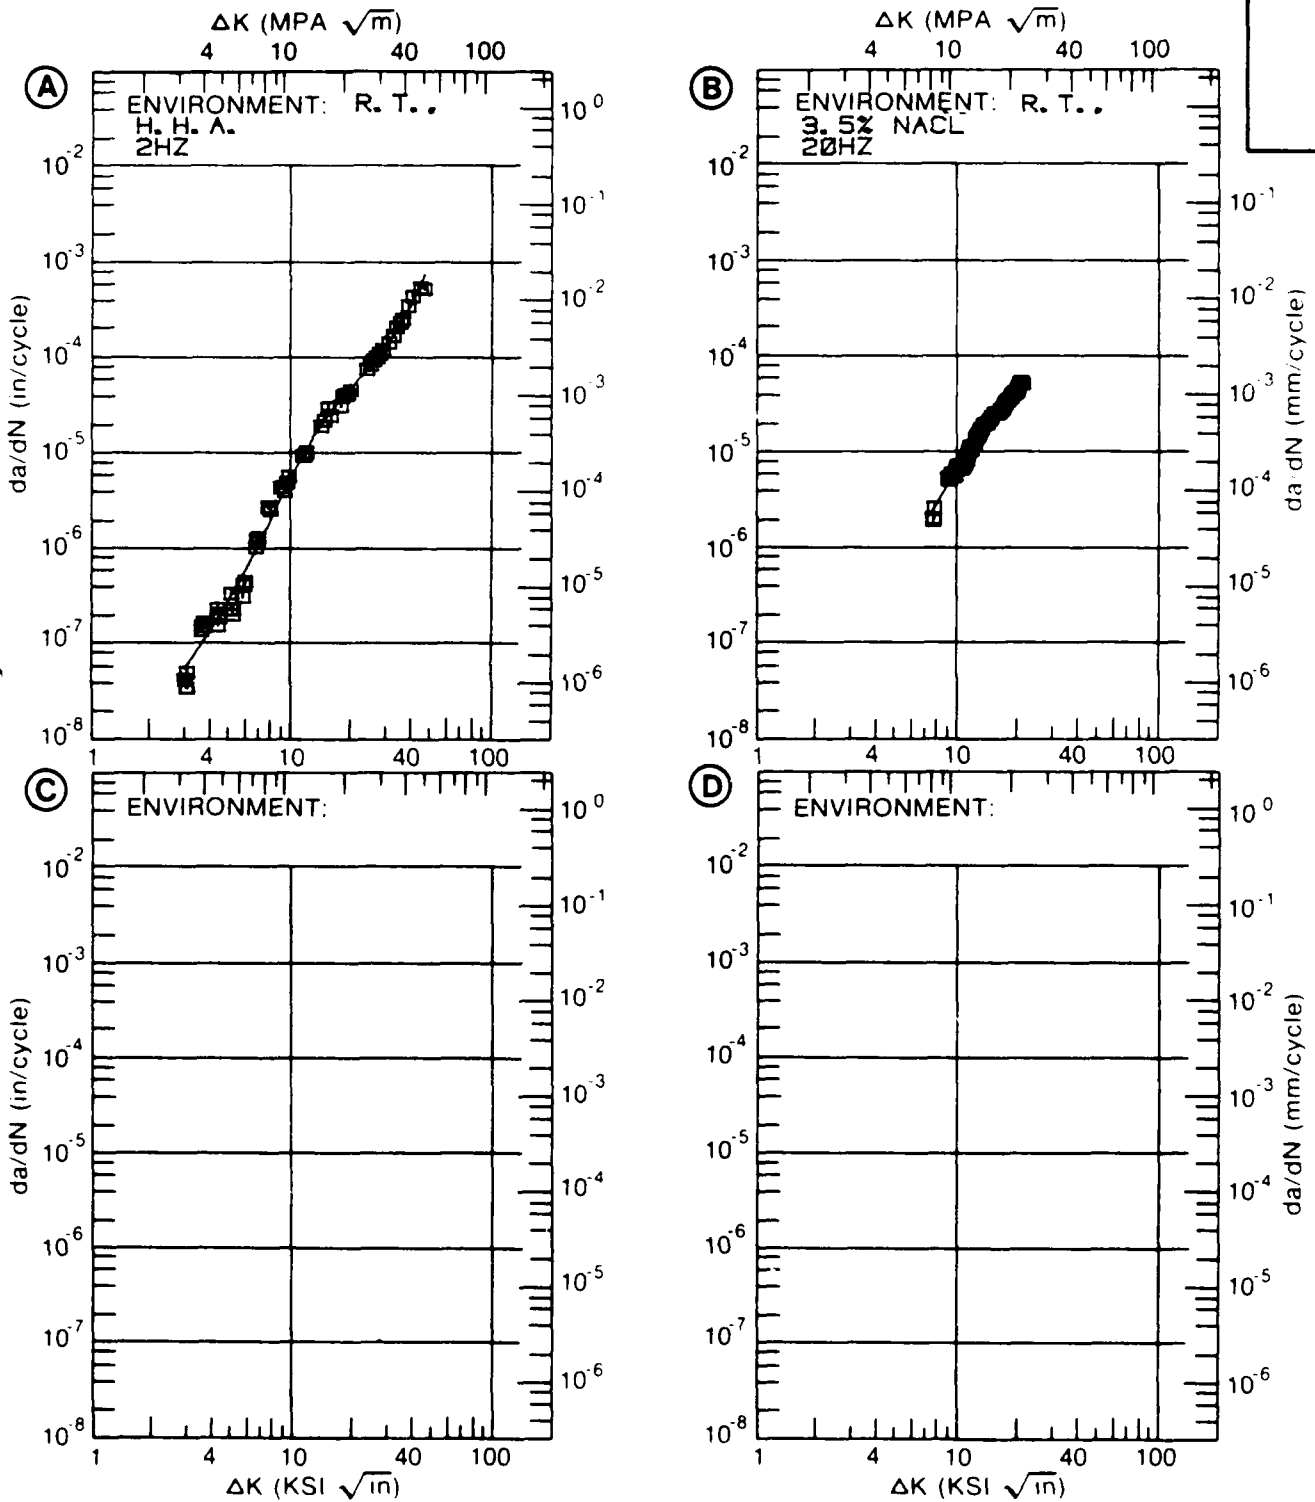


Figure 8.7.3.41

TABLE 8.7.3.42

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.42 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73652					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 6.37	.740			
	B: 6.31		.843		
	C: 6.17			10.1	
	D:				
	7.00	1.10	2.50	11.1	
	8.00	2.24	6.54	18.0	
	9.00	4.57	11.4	26.4	
	10.00	8.91	16.3	31.4	
	13.00	40.5	36.7	49.5	
	16.00	85.7	88.8	107.	
DELTA K MAX	A: 17.47	96.6			
	B: 16.93		117.		
	C: 16.36			122.	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		15.98	10.58	21.77	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0				

CONDITION/HT: T73652
 FORM: 2.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 63.5 KSI
 ULT. STRENGTH: 75.5 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL015

ALUM. ALLOY
7050

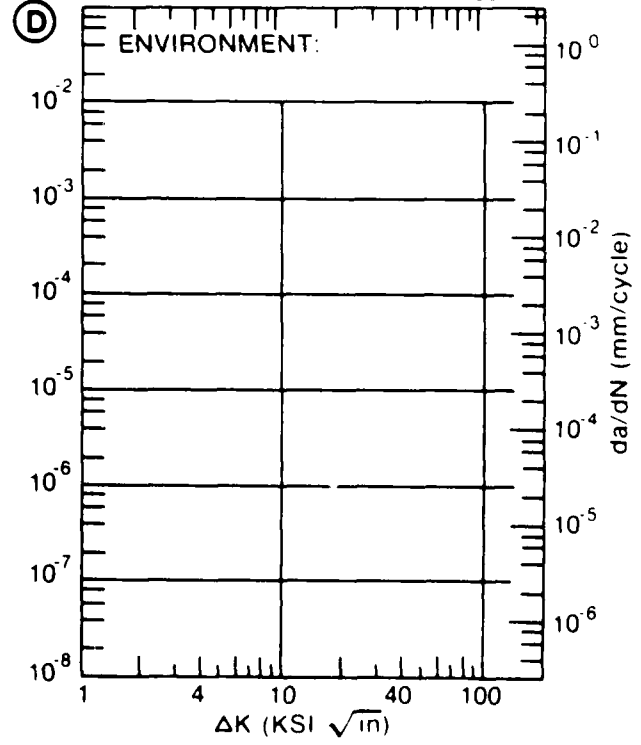
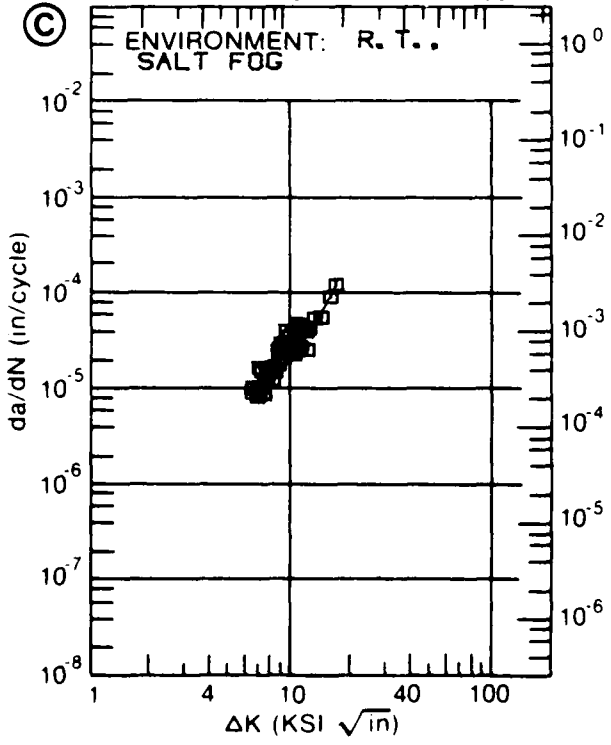
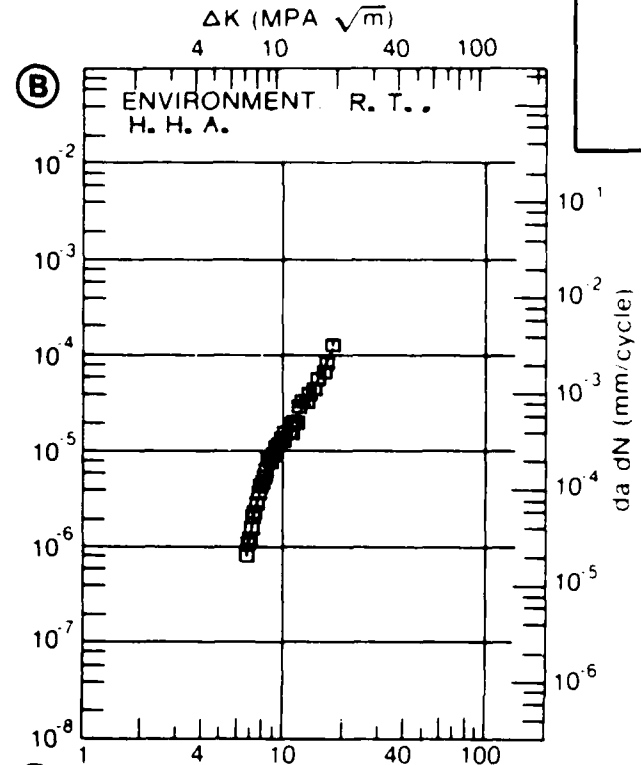
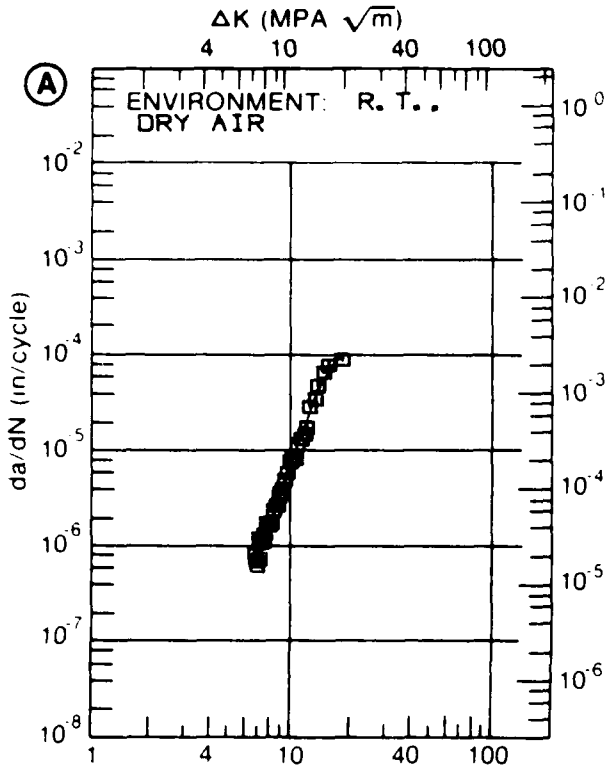


Figure 8.7.3.42

TABLE 8.7.3.43

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.43 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T73652					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K	A: 6.44	1.29			
MIN	B: 6.96		5.74		
	C: 6.41			2.88	
	D:				
	7.00	2.38	5.99	7.40	
	8.00	3.96	18.7	16.2	
	9.00	11.2	36.7	42.6	
DELTA K	A: 9.85	71.6			
MAX	B: 9.64		133.		
	C: 9.89			211.	
	D:				
ROOT MEAN SQUARE		18.75	17.95	27.84	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T73652
 FORM: 7.50" TH FORGING
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 58.1 KSI
 ULT. STRENGTH: 71.0 KSI
 SPECIMEN THK: 1.000"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL015

ALUM.
ALLOY

7050

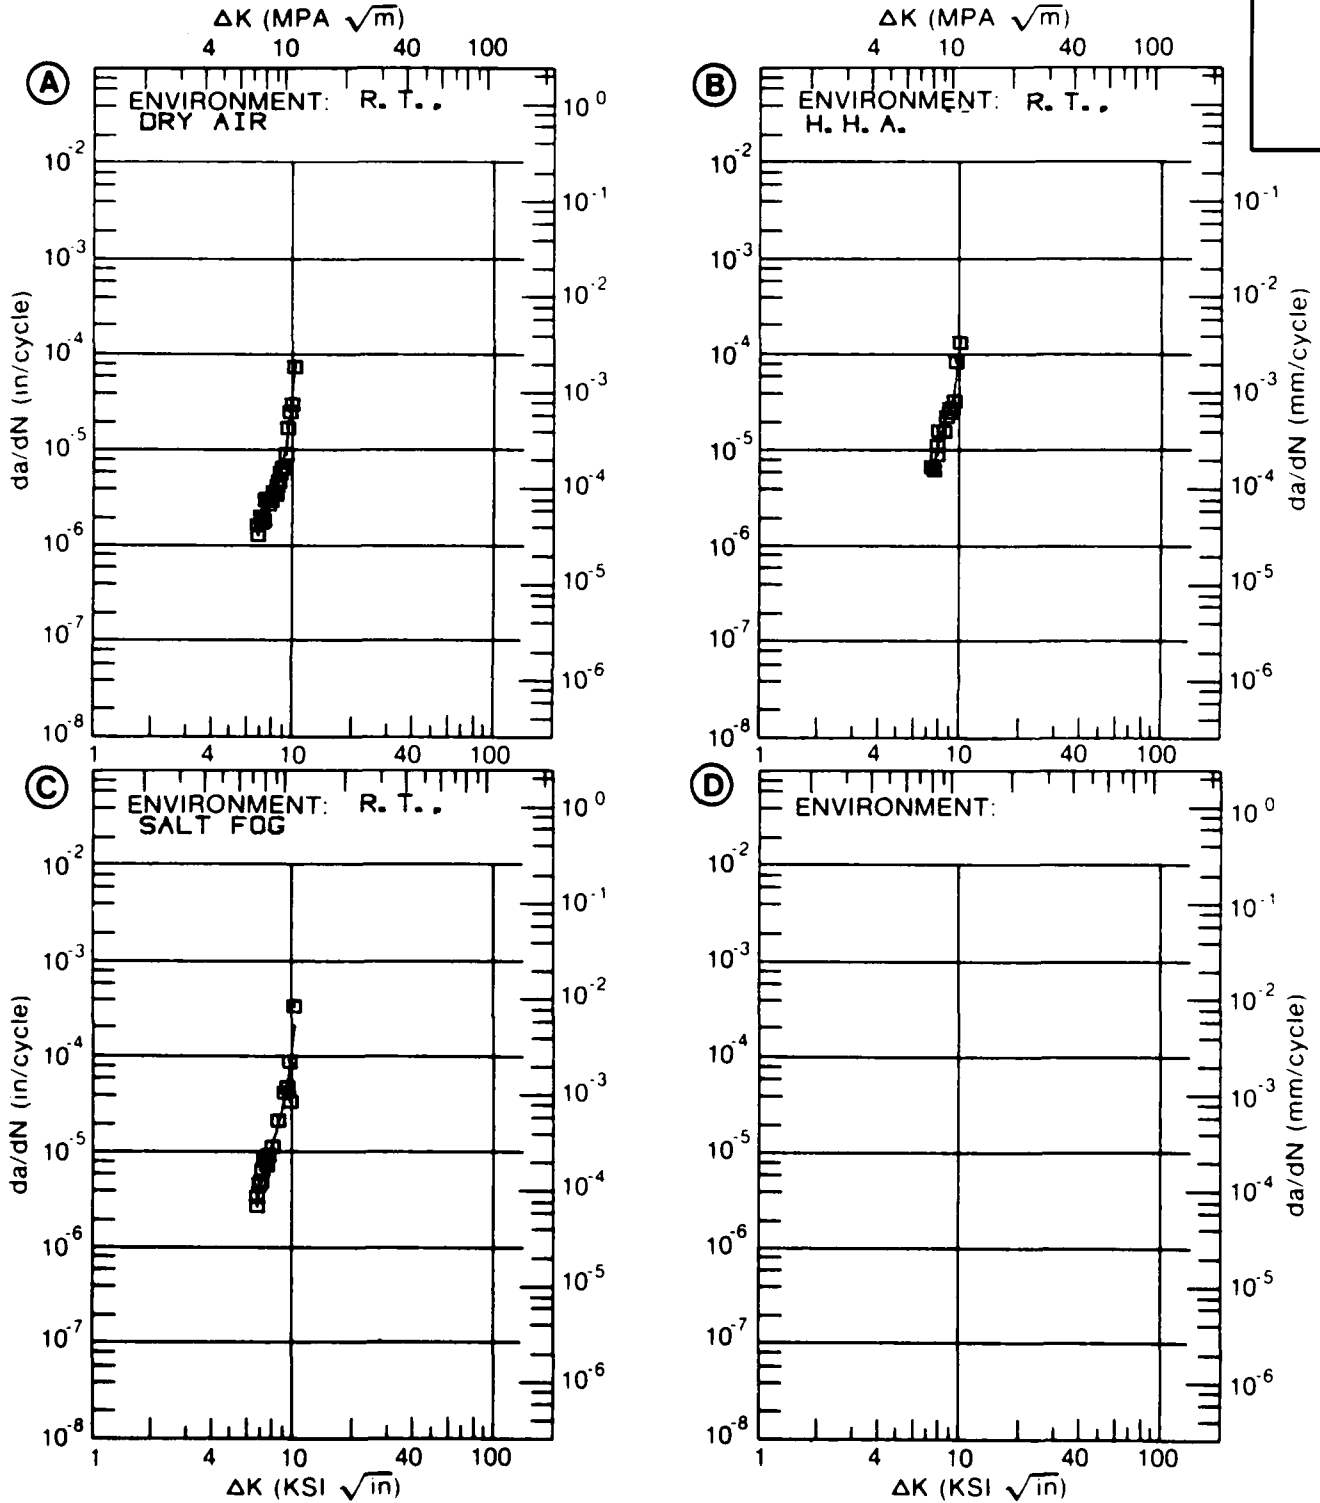


Figure 8.7.3.43

TABLE 8.7.3.44

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.44 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T76					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K	A: 4.84	.857			
MIN	B: 5.01		2.69		
	C: 5.03			3.85	
	D:				
	5.00	.995			
	6.00	2.03	4.50	6.84	
	7.00	3.24	6.62	10.0	
	8.00	4.52	9.35	13.3	
	9.00	5.82	13.0	17.4	
	10.00	7.26	17.6	23.2	
	13.00	18.8	37.4	71.7	
	16.00	86.5	81.2	205.	
DELTA K	A: 16.03	88.0			
MAX	B: 16.84		122.		
	C: 16.00			205.	
	D:				
ROOT MEAN SQUARE		12.34	10.94	17.45	
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T76
 FORM: 0.04" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 13.30 HZ

YIELD STRENGTH: 73.1 KSI
 ULT. STRENGTH: 81.0 KSI
 SPECIMEN THK: 0.040"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: AL015

ALUM.
 ALLOY
 7050

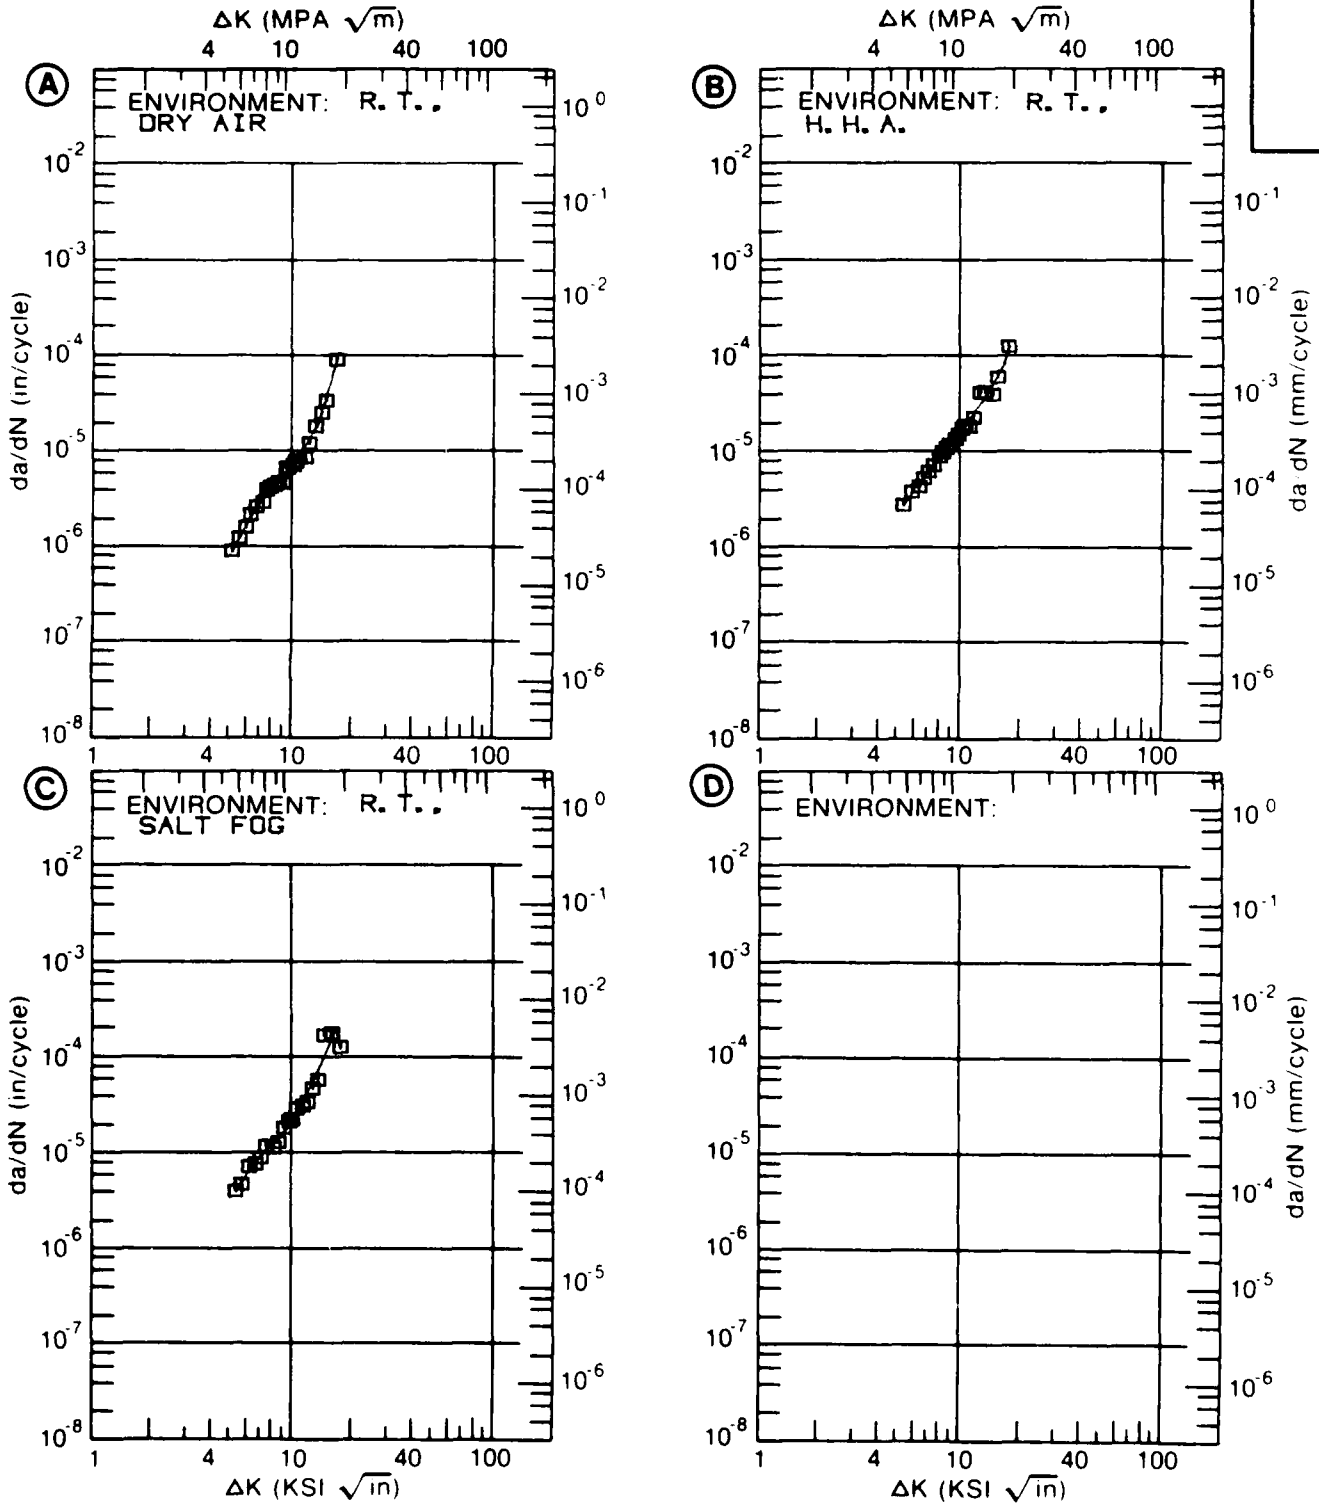


Figure 8.7.3.44

TABLE 8.7.3.45

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.45 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7050
CONDITION: T/6
ENVIRONMENT: R T , LAB AIR

DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)			
		A	B	C	D
		R=+0.00	R=+0.33		
DELTA K	A: 8.71	5.35			
MIN	B: 5.75		2.58		
	C:				
	D:				
	6.00		2.88		
	7.00		4.27		
	8.00		5.96		
	9.00	5.82	7.99		
	10.00	7.60	10.4		
	13.00	14.4	20.4		
	16.00	23.5	36.1		
	20.00	40.1	70.3		
	25.00	69.8	148.		
	30.00	113.	290.		
	35.00	174.			
	40.00	260.			
DELTA K	A: 40.58	272.			
MAX	B: 30.93		327.		
	C:				
	D:				

ROOT MEAN SQUARE 5.60 9.29
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2 4
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T76
 FORM: 0.09" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 FREQUENCY: 13.30 HZ
 ENVIRONMENT: R. T., LAB AIR

YIELD STRENGTH: 79.0 KSI
 ULT. STRENGTH: 85.8 KSI
 SPECIMEN THK: 0.090- 0.091"
 SPECIMEN WIDTH: 4.000- 4.004"
 REFERENCES: 86213

ALUM. ALLOY
7050

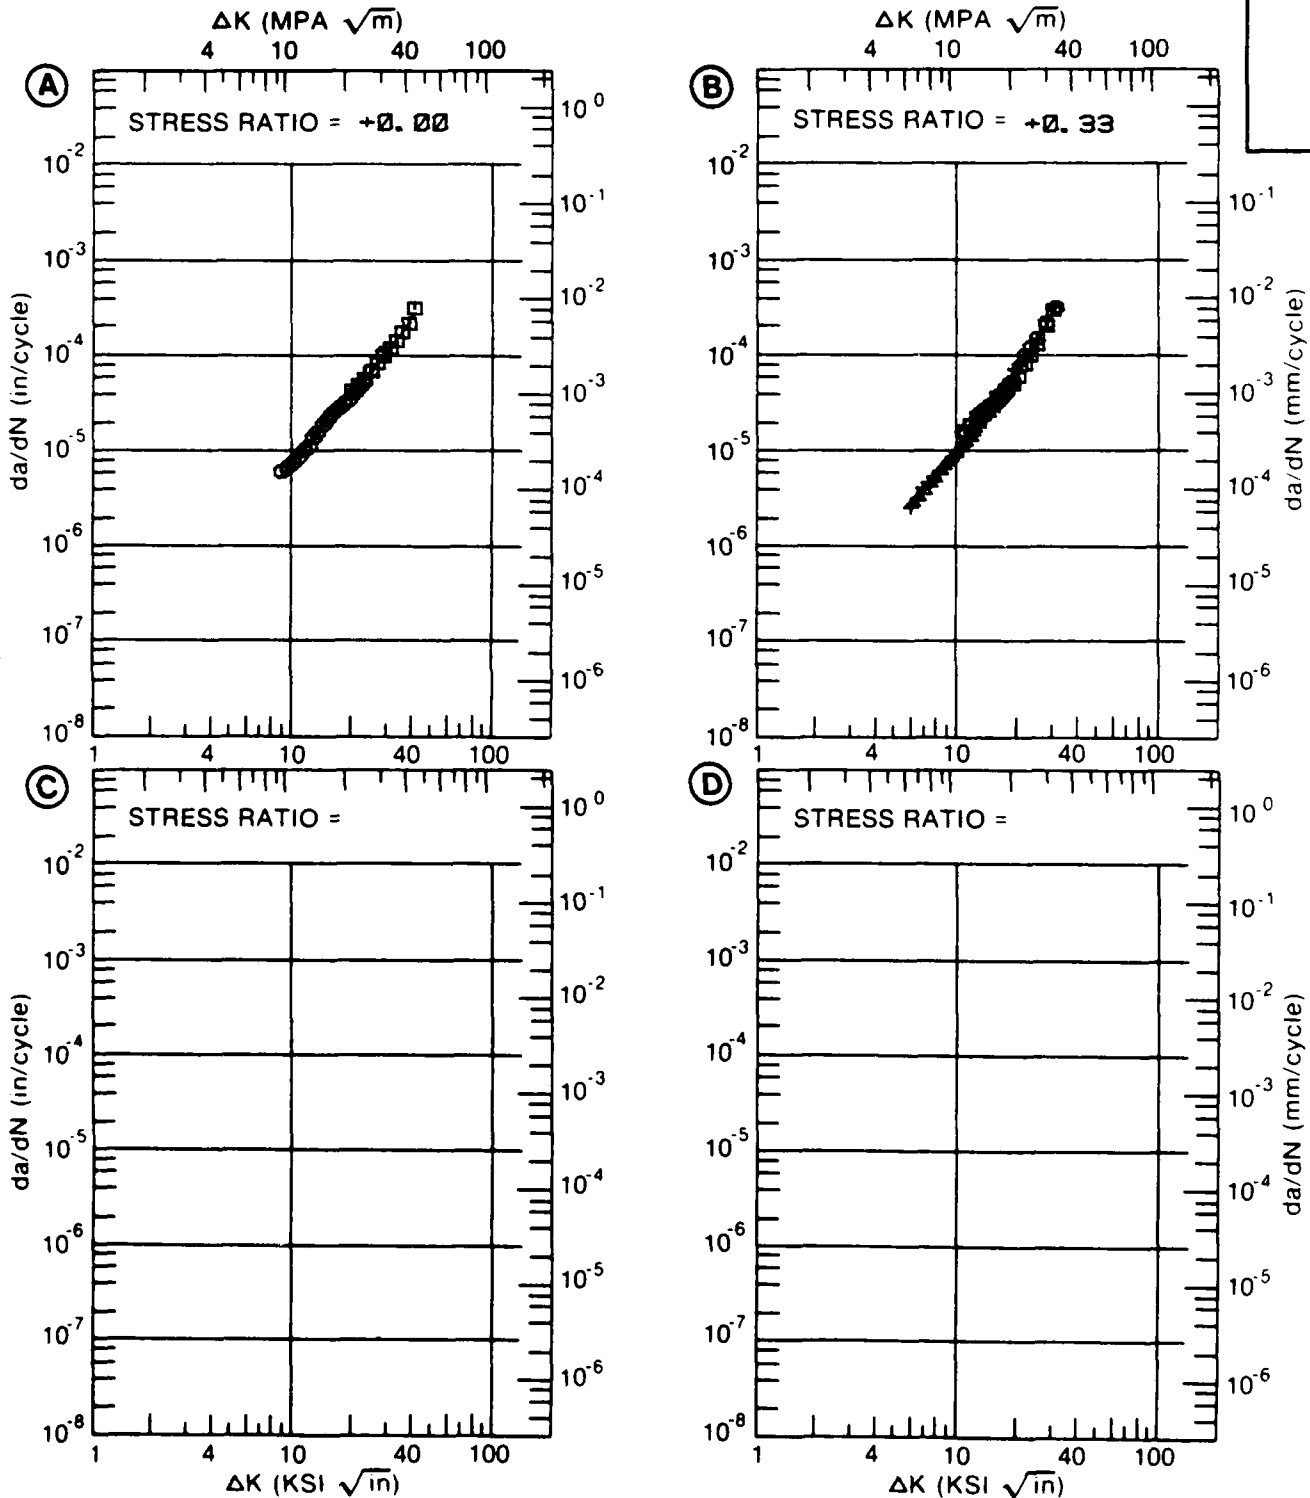


Figure 8.7.3.45

TABLE 8.7.3.46

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.46 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T76					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. DRY AIR	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.13	1.36			
	B: 5.17		3.52		
	C: 5.14			3.98	
	D:				
	6.00	2.91	5.56	7.49	
	7.00	4.97	8.84	12.6	
	8.00	7.72	13.2	18.7	
	9.00	10.9	19.0	25.5	
	10.00	14.0	26.7	33.3	
	13.00	24.6	66.2	65.3	
	16.00		151.	121.	
DELTA K MAX	A: 15.70	88.1			
	B: 17.18		206.		
	C: 17.27			158.	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		13.89	12.44	8.81	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 2.0				

CONDITION/HT: T76
 FORM: Ø. 13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 13.30 HZ

YIELD STRENGTH: 79.6 KSI
 ULT. STRENGTH: 83.6 KSI
 SPECIMEN THK: Ø. 125"
 SPECIMEN WIDTH: 4.000"
 REFERENCES: ALØ15

ALUM.
ALLOY

7050

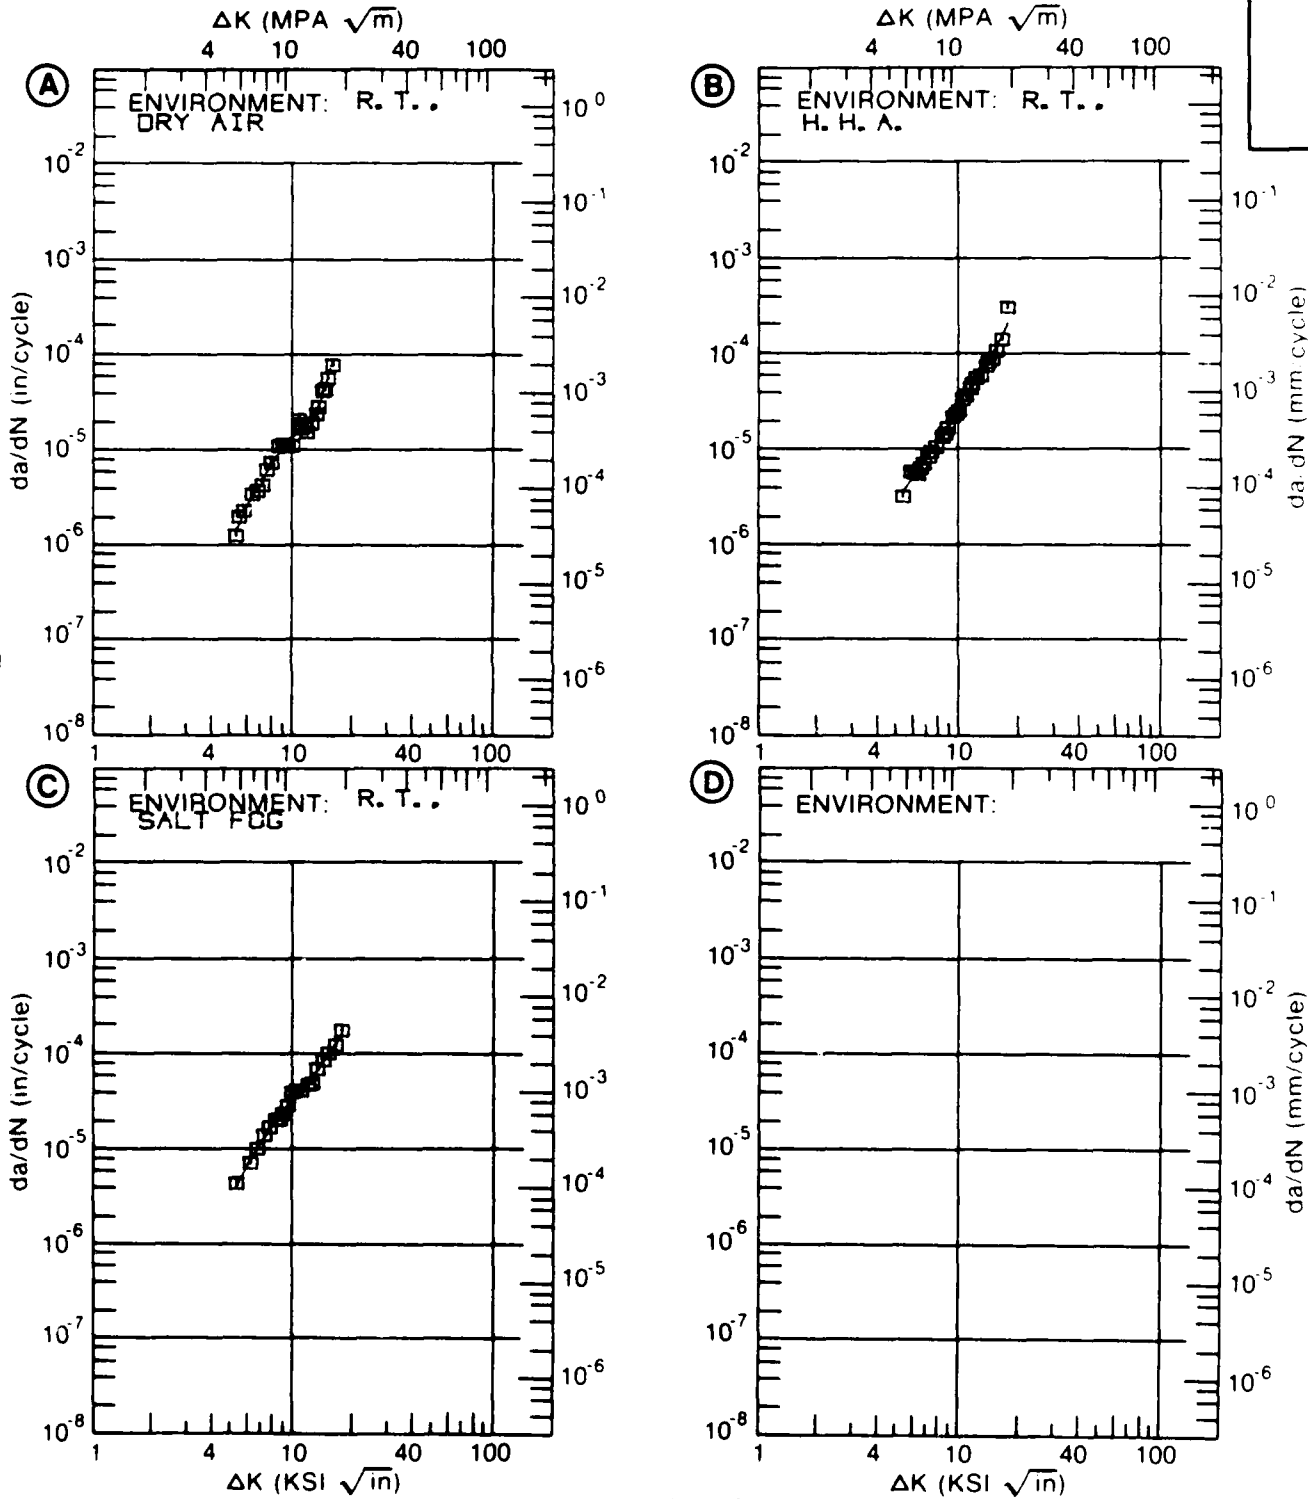


Figure 8.7.3.46

TABLE 8.7.3.47

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.47 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T7651					
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN./CYCLE)			
		A	B	C	D
		E= R. T. H. H. A., 2HZ	E= R. T. H. H. A., 20HZ	E= R. T. 3. 5% NAACL, 2HZ	E= R. T. 3. 5% NAACL, 20HZ
DELTA K MIN	A: 5.39	.674			
	B: 3.50		.131		
	C: 8.21			13.8	
	D: 3.50				.0943
	4.00		.183		.279
	5.00		.330		1.26
	6.00	1.39	.700		3.35
	7.00	2.75	1.73		6.64
	8.00	4.05	3.74		11.0
	9.00	5.43	6.50	17.4	16.1
	10.00	7.27	9.75	23.0	21.8
	13.00	17.0	21.3	46.5	41.2
	16.00	35.0	35.5	80.4	63.8
	20.00	70.8	52.1	141.	102.
	25.00	146.		247.	172.
	30.00	292.		399.	288.
	35.00	603.		628.	
	40.00	1297.		1018.	
	50.00			4127.	
DELTA K MAX	A: 47.21	4197.			
	B: 21.86		55.9		
	C: 53.64			11027.	
	D: 31.41				334.
ROOT MEAN SQUARE PERCENT ERROR		8.88	10.99	10.29	12.41
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1	1

CONDITION/HT: T7651
 FORM: 0.52" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY:

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.147- 0.148"
 SPECIMEN WIDTH: 3.000"
 REFERENCES: 86844

ALUM. ALLOY
7050

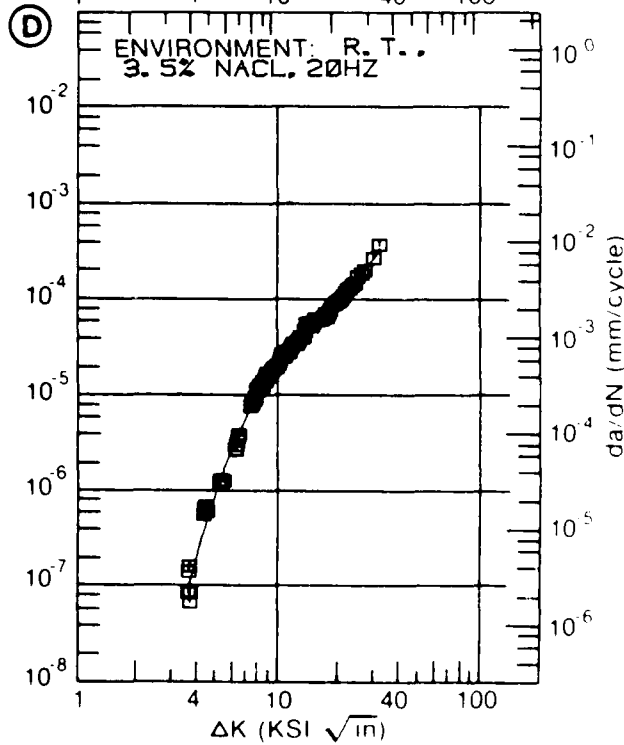
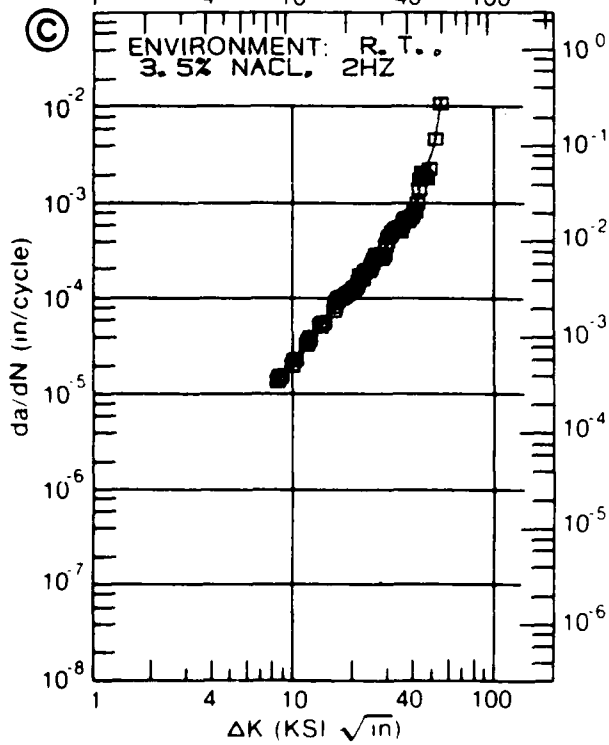
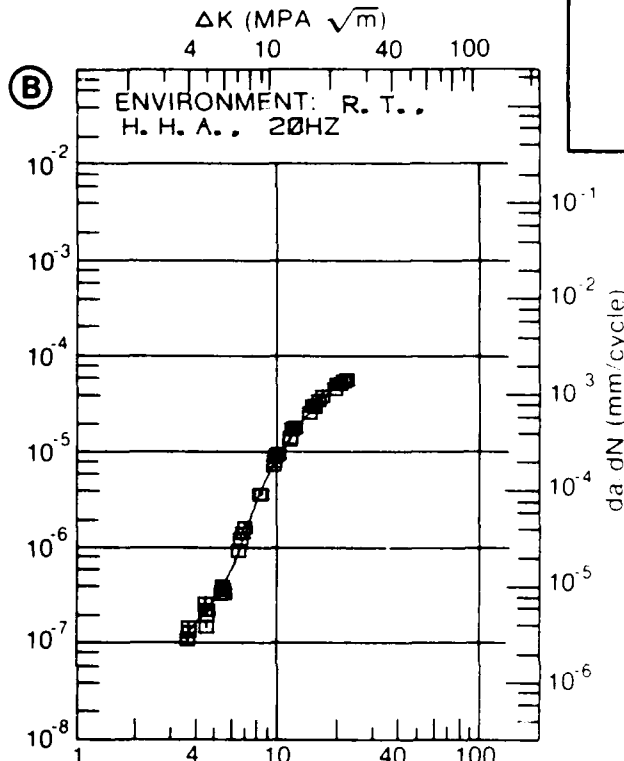
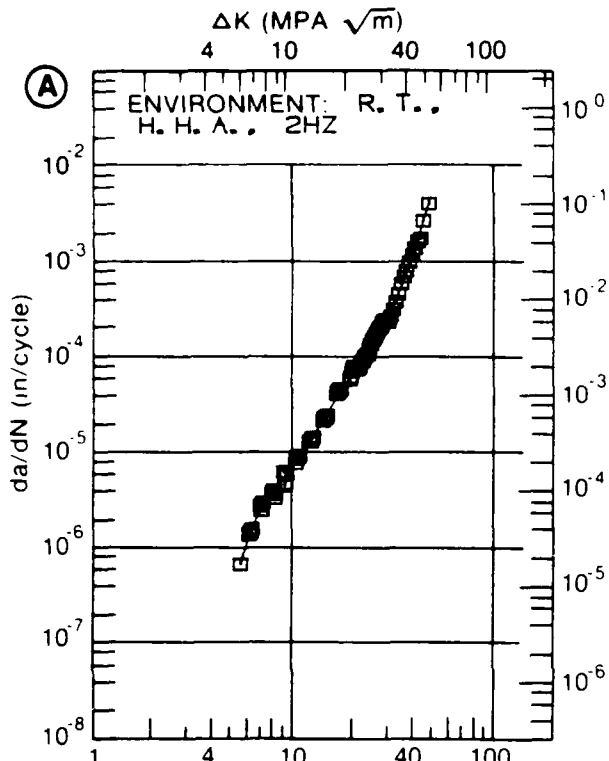


Figure 8.7.3.47

TABLE 8.7.3.48

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.48 INDICATING EFFECT

OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7651

DELTA K (KSI*IN**1/2)	DA/DN (10** ⁻⁶ IN./CYCLE)			
	A	B	C	D
	E= R. T. 3. 5% NAACL			
A: 5.35	977			
DELTA K B:				
MIN C:				
D:				
6.00	2.51			
7.00	6.46			
8.00	11.6			
9.00	17.2			
10.00	22.9			
13.00	44.1			
16.00	88.5			
A: 16.69	106			
DELTA K B:				
MAX C:				
D:				

ROOT MEAN SQUARE 11.47
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T7651
 FORM: 1.13" TH PLATE
 SPECIMEN TYPE:
 ORIENTATION:
 STRESS RATIO: +0.10
 FREQUENCY: 1.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91332

ALUM. ALLOY
7050

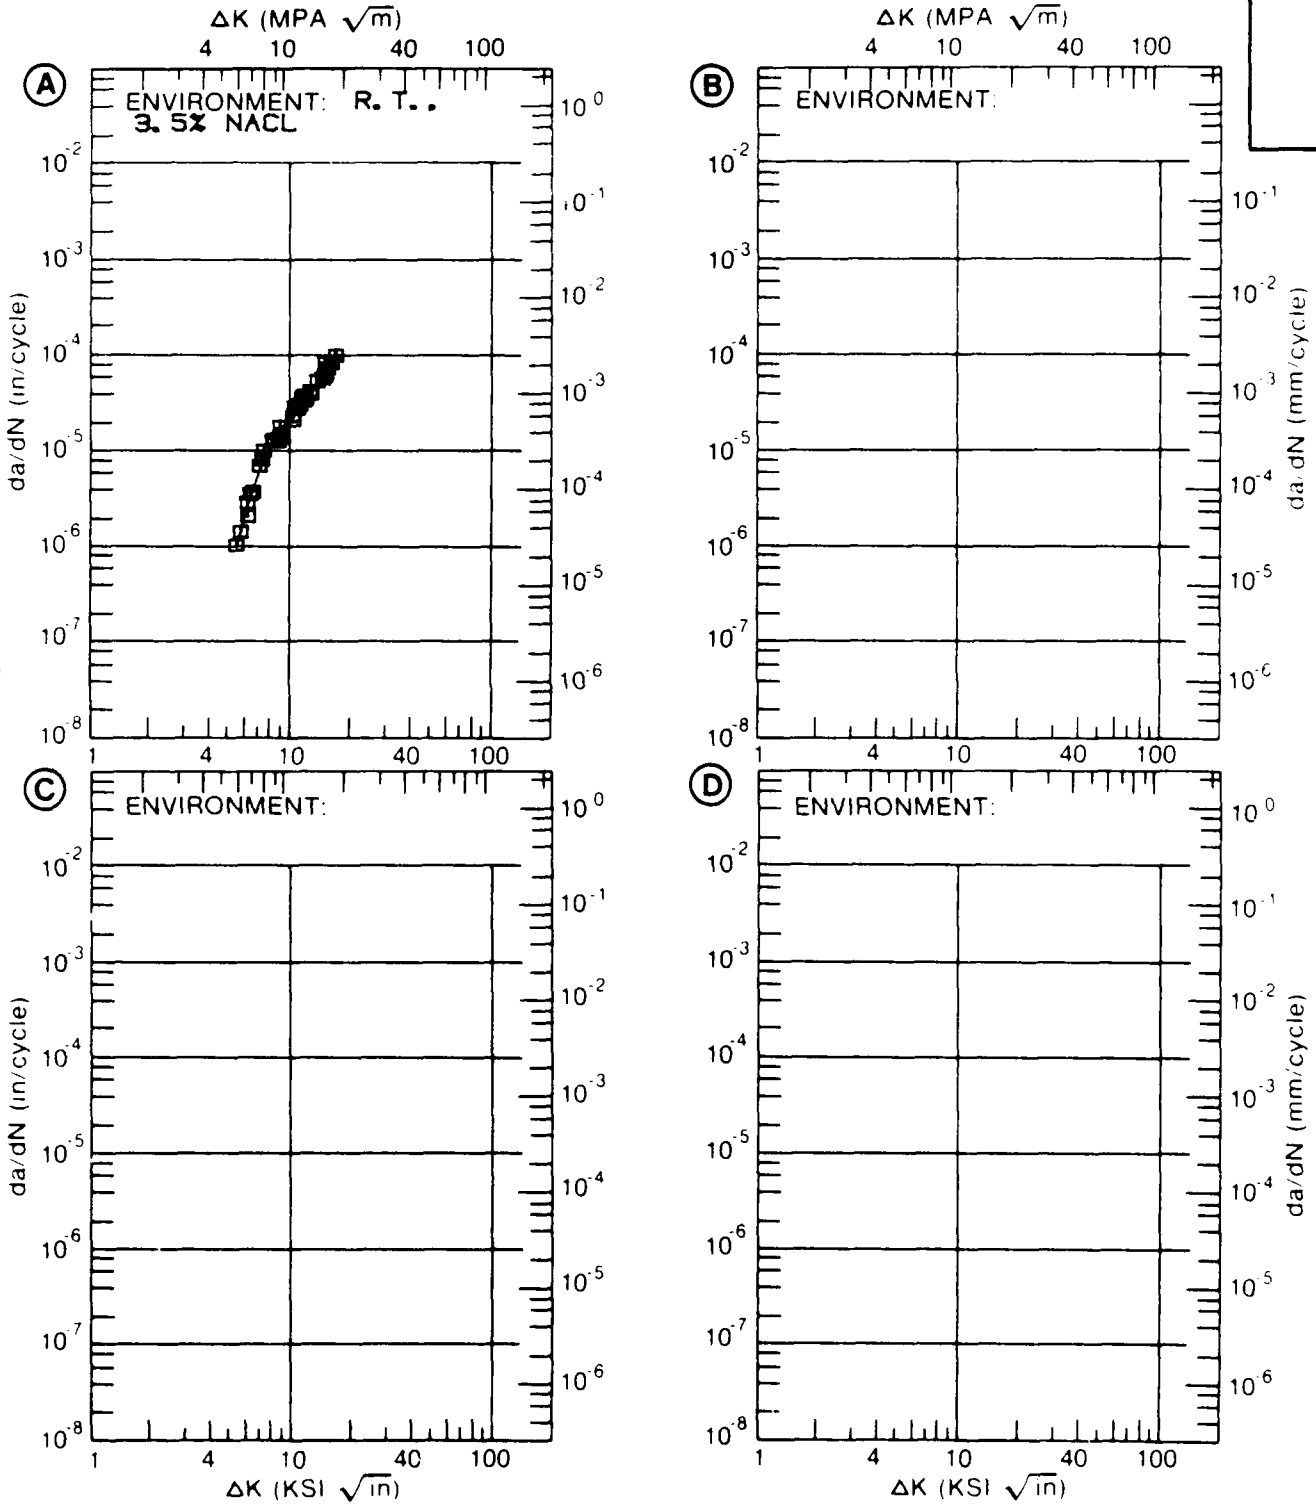


Figure 8.7.3.48

TABLE 8.7.3.49

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE INDICATING EFFECT
OF ENVIRONMENT

MATERIAL ALUMINUM 7050
CONDITION: T7651

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. I. DRY AIR			
DELTA K MIN	A: 6.45	2.45			
	B:				
	C:				
	D:				
	7.00	3.63			
	8.00	5.78			
	9.00	7.70			
	10.00	9.43			
	13.00	15.6			
	16.00	23.9			
	20.00	41.0			
DELTA K MAX	A: 24.59	98.5			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 6.62
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T7651
 FORM: 1.13" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.10
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK:
 SPECIMEN WIDTH:
 REFERENCES: 91332

ALUM.
ALLOY

7050

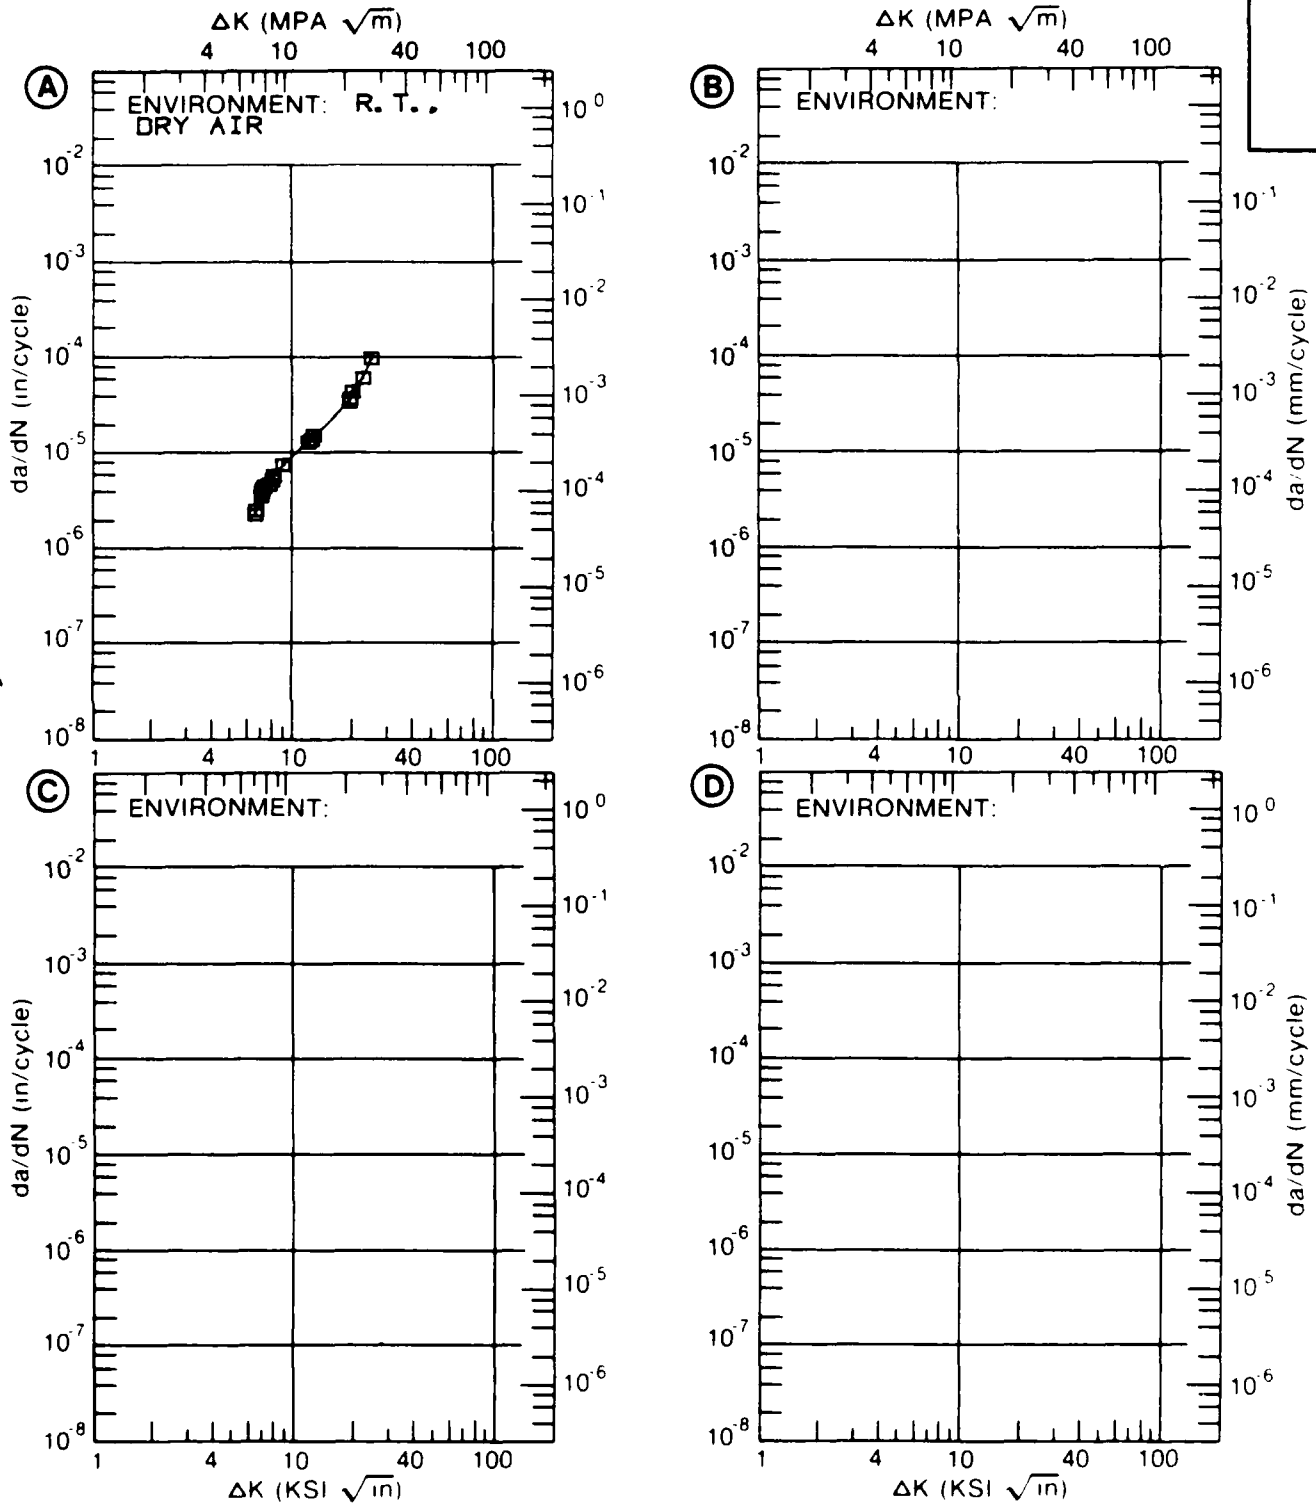


Figure 8.7.3.4

TABLE 8.7.3.50

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.50 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7651

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN. /CYCLE)			
	A	B	C	D
	E= R. T. LAB AIR	E= R. T. SIM SEA WATER	E= R. T. JP-4 FUEL	
DELTA K MIN	A: 4.08 : B: 5.62 : C: 5.00 : D:	.107	.807	.514
	5.00 : 6.00 : 7.00 : 8.00 : 9.00 : 10.00 : 13.00 : 16.00 : 20.00 : 25.00 :	.580 1.55 2.92 4.57 6.33 8.04 12.0 14.6 22.9 74.6	.980 1.77 3.31 6.06 10.6 27.6 35.8 64.2 446.	.920 1.08 1.41 2.23 3.61 9.18 16.4 34.1 105.
DELTA K MAX	A: 26.13 : B: 26.23 : C: 25.28 : D:	107.	906.	112.
ROOT MEAN SQUARE PERCENT ERROR	21.58	24.09	13.59	

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25
SUMMARY 1.25-2.0
(NP/NA) >2.0

CONDITION/HT: T7651
 FORM: 1.25" TH PLATE
 SPECIMEN TYPE: WOL
 ORIENTATION: L-T
 STRESS RATIO: +0.02
 FREQUENCY: 1.00- 20.00 HZ

YIELD STRENGTH: 73.8 KSI
 ULT. STRENGTH: 81.0 KSI
 SPECIMEN THK: 1.250"
 SPECIMEN WIDTH: 5.000"
 REFERENCES: MA005

ALUM. ALLOY
7050

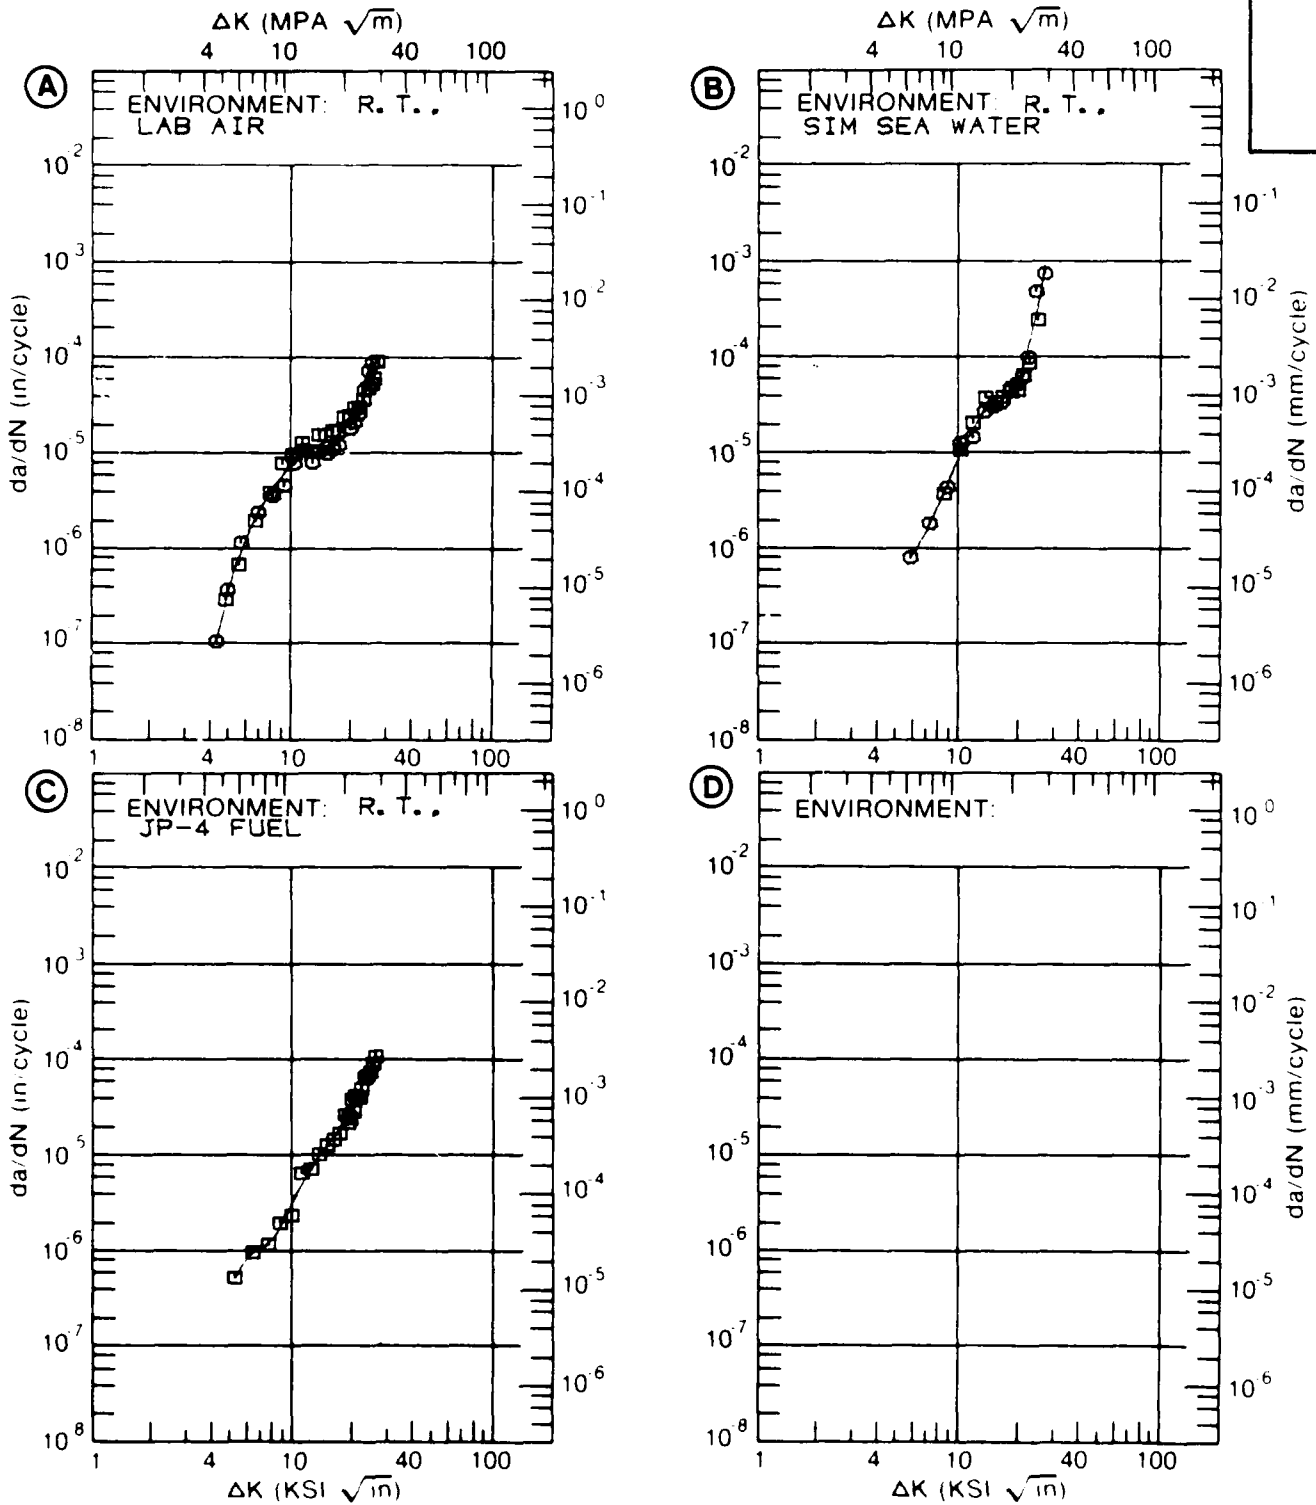


Figure 8.7.3.5a

TABLE 8.7.3.51

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.51 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050	
CONDITION: T7651X			
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN. /CYCLE)	
		A	B
		E= R. T. L. H. A.	E= R. T. H. H. A.
DELTA K	A: 4.11	.389	
MIN	B: 4.21		.827
	C:		
	D:		
	5.00	.505	1.68
	6.00	.701	3.32
	7.00	.986	5.65
	8.00	1.44	8.66
	9.00	2.22	12.3
	10.00	3.49	16.6
	13.00	10.2	32.3
	16.00	20.9	
DELTA K	A: 18.19	33.7	
MAX	B: 15.62		49.0
	C:		
	D:		
ROOT MEAN SQUARE		12.45	4.55
PERCENT ERROR			
LIFE PREDICTION	0.0-0.5		
RATIO	0.5-0.8		
SUMMARY (NP/NA)	0.8-1.25	2	1
	1.25-2.0		
	>2.0		

CONDITION/HT: T7651X
 FORM: 0.91" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: 0.900"
 SPECIMEN WIDTH: 3.100- 3.805"
 REFERENCES: AL008

ALUM. ALLOY
7050

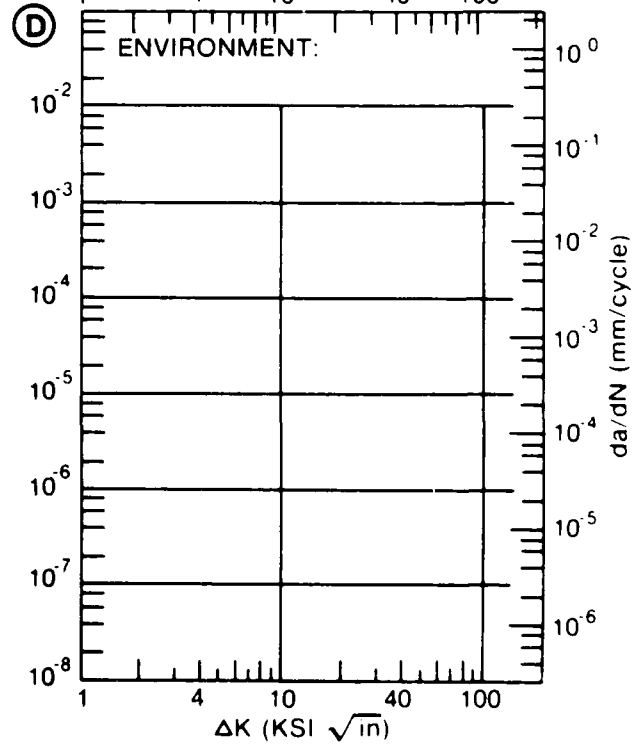
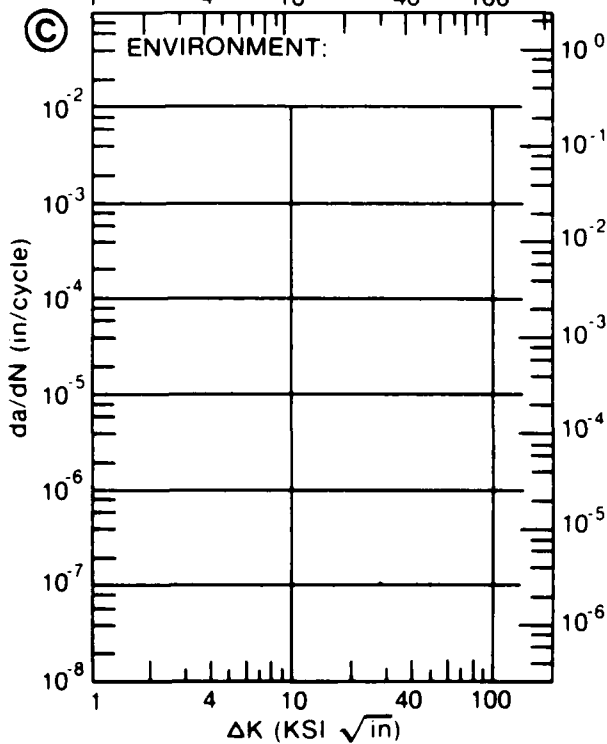
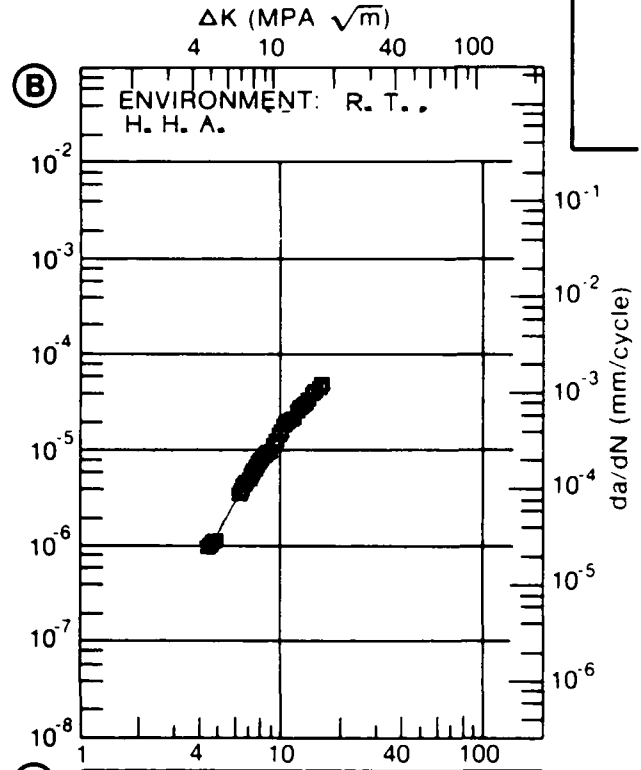
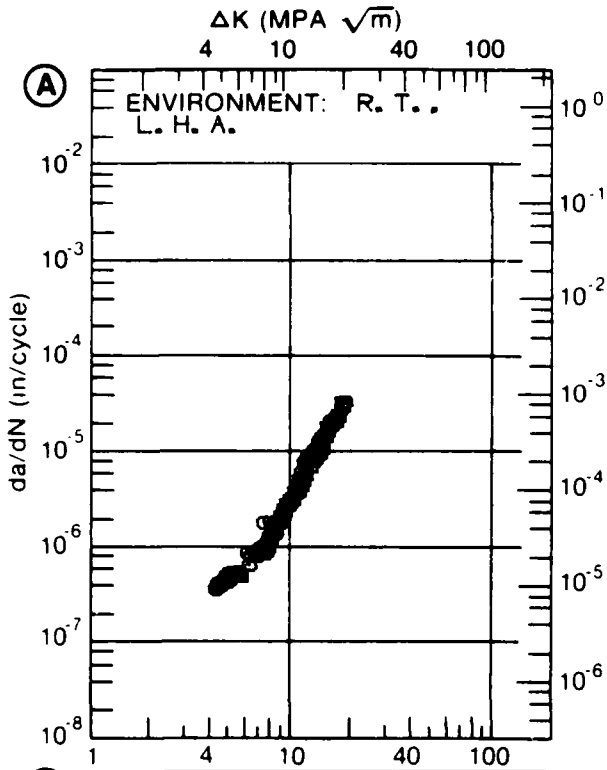


Figure 8.7.3.51

TABLE 8.7.3.52

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.52 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM 7050
CONDITION: T7651X

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.	E= R. T. H. H. A.		
DELTA K A: 4.41	417			
MIN B: 3.25		140		
C:				
D:				
3.50		168		
4.00		436		
5.00	880	2.05		
6.00	1.62	4.44		
7.00	2.39	6.91		
8.00	3.26	9.47		
9.00	4.31	12.6		
10.00	5.65	17.0		
13.00	13.3			
16.00	35.6			
DELTA K A: 16.78	46.8			
MAX B: 10.01		17.0		
C:				
D:				

ROOT MEAN SQUARE 9.49 13.76
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 2 2
SUMMARY 1.25-2.0
(NP/NA) 2.0

CONDITION/HT: T7651X
 FORM: Ø. 91" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 20.00 HZ

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: Ø. 900"
 SPECIMEN WIDTH: 3.805"
 REFERENCES: AL008

ALUM.
 ALLOY
 7050

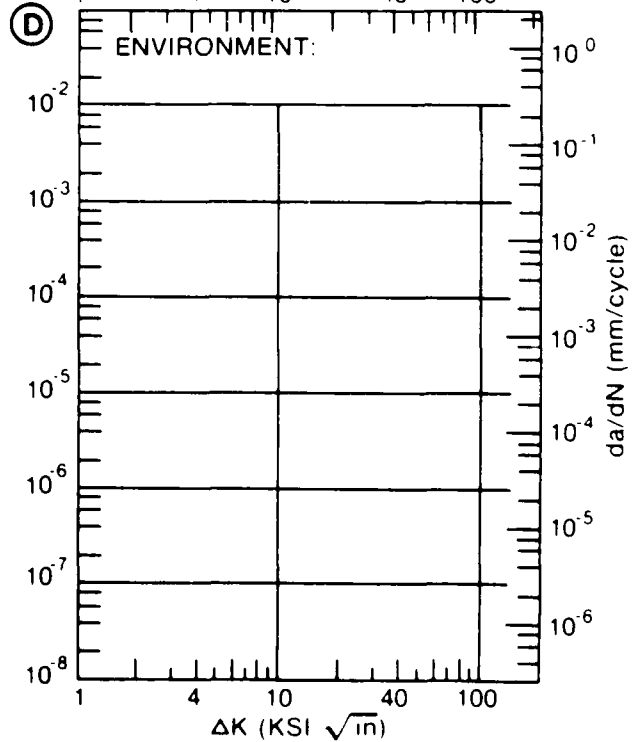
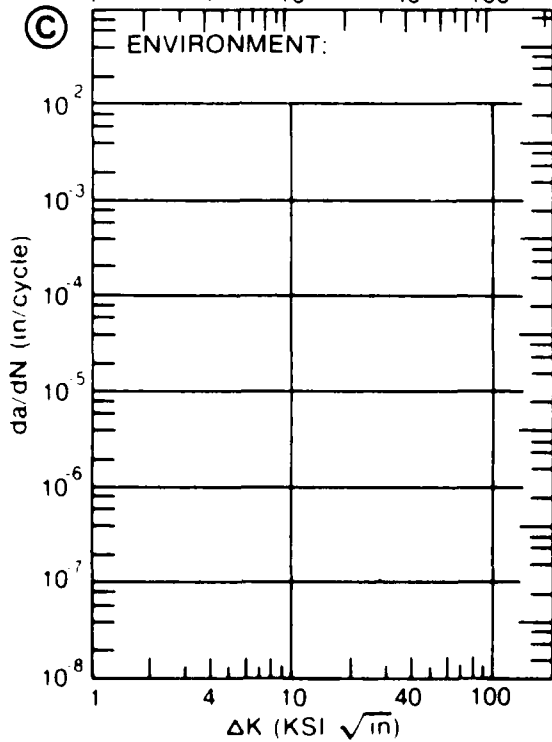
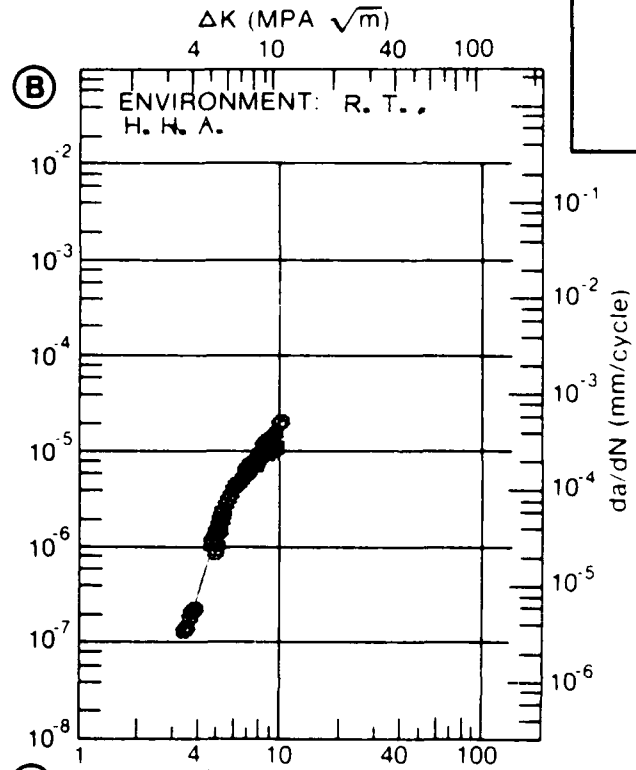
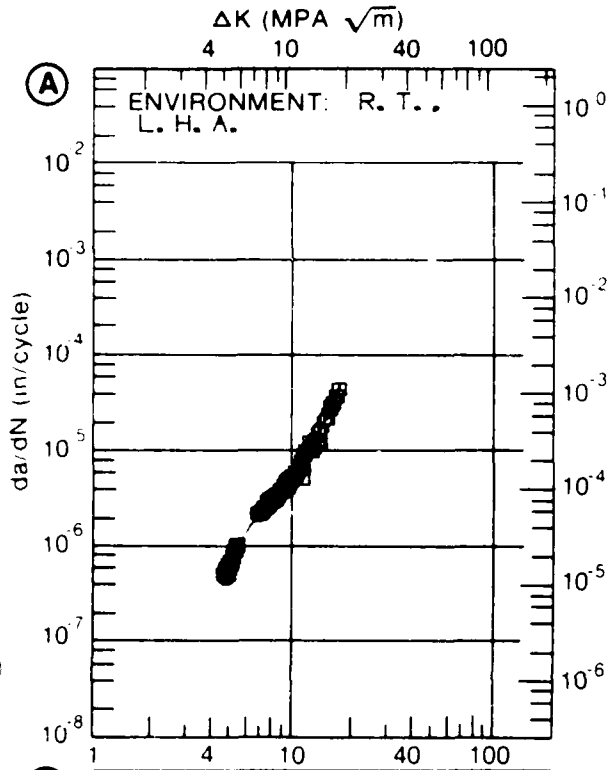


Figure 8.7.3.52

TABLE 8.7.3.93

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.53 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM		7050			
CONDITION: T76511					
ENVIRONMENT: R T		H H A			
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN./CYCLE)			
		A	B	C	D
		R=+0.33			
DELTA K	A: 7.24	6.34			
MIN	B:				
	C:				
	D:				
	8.00 :	9.91			
	9.00 :	13.0			
	10.00 :	15.7			
	13.00 :	44.4			
DELTA K	A: 14.85	73.1			
MAX	B:				
	C:				
	D:				
ROOT MEAN SQUARE		14.39			
PERCENT ERROR					
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25				
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T76511
 FORM: 6.00" TH PLATE
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 FREQUENCY: 18.30 HZ
 ENVIRONMENT: R. T., H. H. A.

YIELD STRENGTH: 59.1 KSI
 ULT. STRENGTH: 70.5 KSI
 SPECIMEN THK: 0.998"
 SPECIMEN WIDTH: 3.801"
 REFERENCES: AL004

ALUM. ALLOY
7050

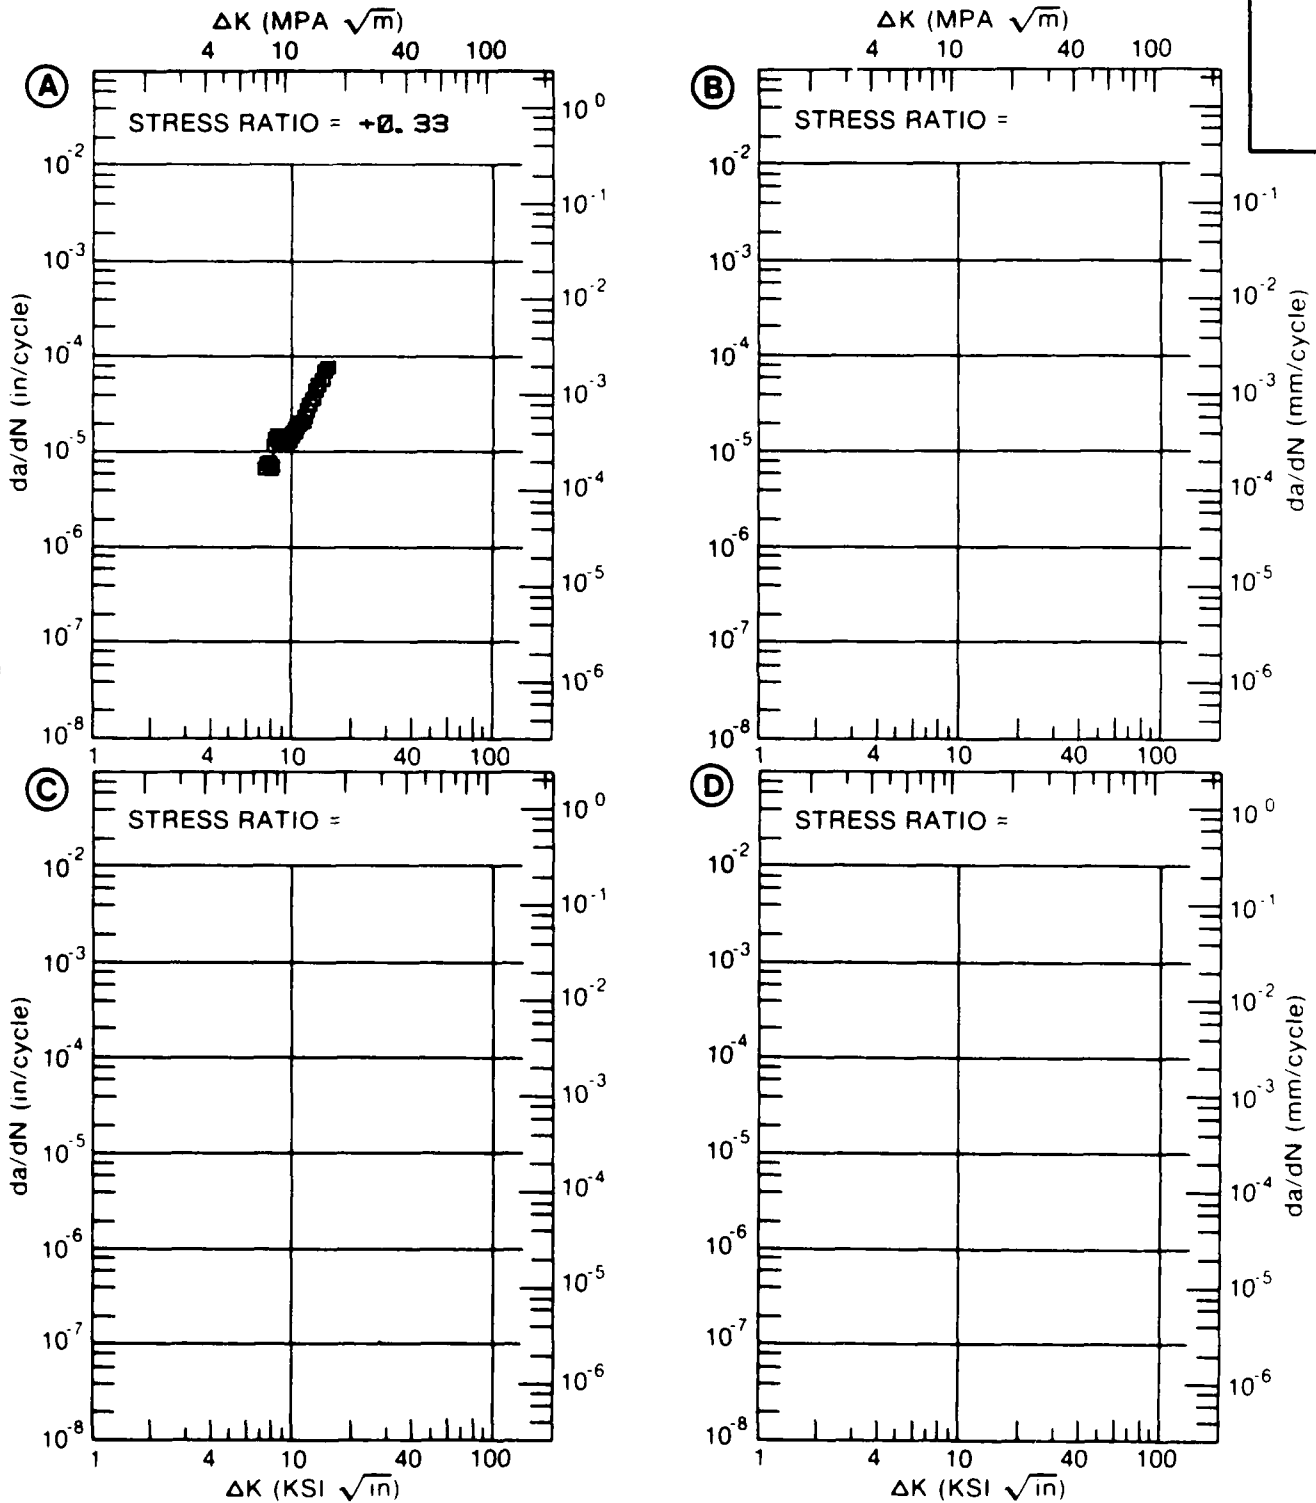


Figure 8.7.3.53

TABLE 8.7.3.54

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 8.7.3.54 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050				
CONDITION: T76511						
DELTA K (KSI*IN**1/2)		DA/DN (10**--6 IN./CYCLE)				
		A	B	C	D	
		E= R.T. H. H. A. 2HZ	E= R.T. H. H. A. 20HZ	E= R.T. 3. 5% NAACL 2HZ	E= R.T. 3. 5% NAACL 20HZ	
DELTA K MIN	A:	6.23	.778			
	B:	4.28	.146			
	C:	6.83		1.29		
	D:	3.12			.005	
		3.50			.0279	
		4.00			.123	
		5.00		.152	.467	
		6.00		.310	.772	
		7.00	1.26	.735	1.25	1.41
		8.00	2.11	1.53	2.06	3.38
		9.00	3.25	2.76	5.26	7.86
	10.00	4.71	4.47	11.6	15.0	
	13.00	11.3	12.6	42.9	44.1	
	16.00	22.2	24.9	93.6	71.3	
	20.00	46.3	46.8	181.	99.5	
	25.00	100.	81.3	304.	138.	
	30.00	198.	123.	436.	205.	
	35.00	369.	175.	576.	338.	
	40.00	660.		732.		
	50.00	1946.		1117.		
DELTA K MAX	A:	56.19	3645.			
	B:	37.08	212.			
	C:	59.30		1619.		
	D:	35.92			375.	
ROOT MEAN SQUARE		19.51	14.25	11.29	20.13	
PERCENT ERROR						
LIFE	0.0-0.5					
PREDICTION	0.5-0.8					
RATIO	0.8-1.25	1	1	1		
SUMMARY	1.25-2.0				1	
(NP/NA)	2.0					

CONDITION/HT: T76511
 FORM: Ø. 44" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +Ø. 1Ø
 FREQUENCY:

YIELD STRENGTH:
 ULT. STRENGTH:
 SPECIMEN THK: Ø. 151- Ø. 152"
 SPECIMEN WIDTH: 3. ØØØ"
 REFERENCES: 86844

ALUM. ALLOY
7Ø5Ø

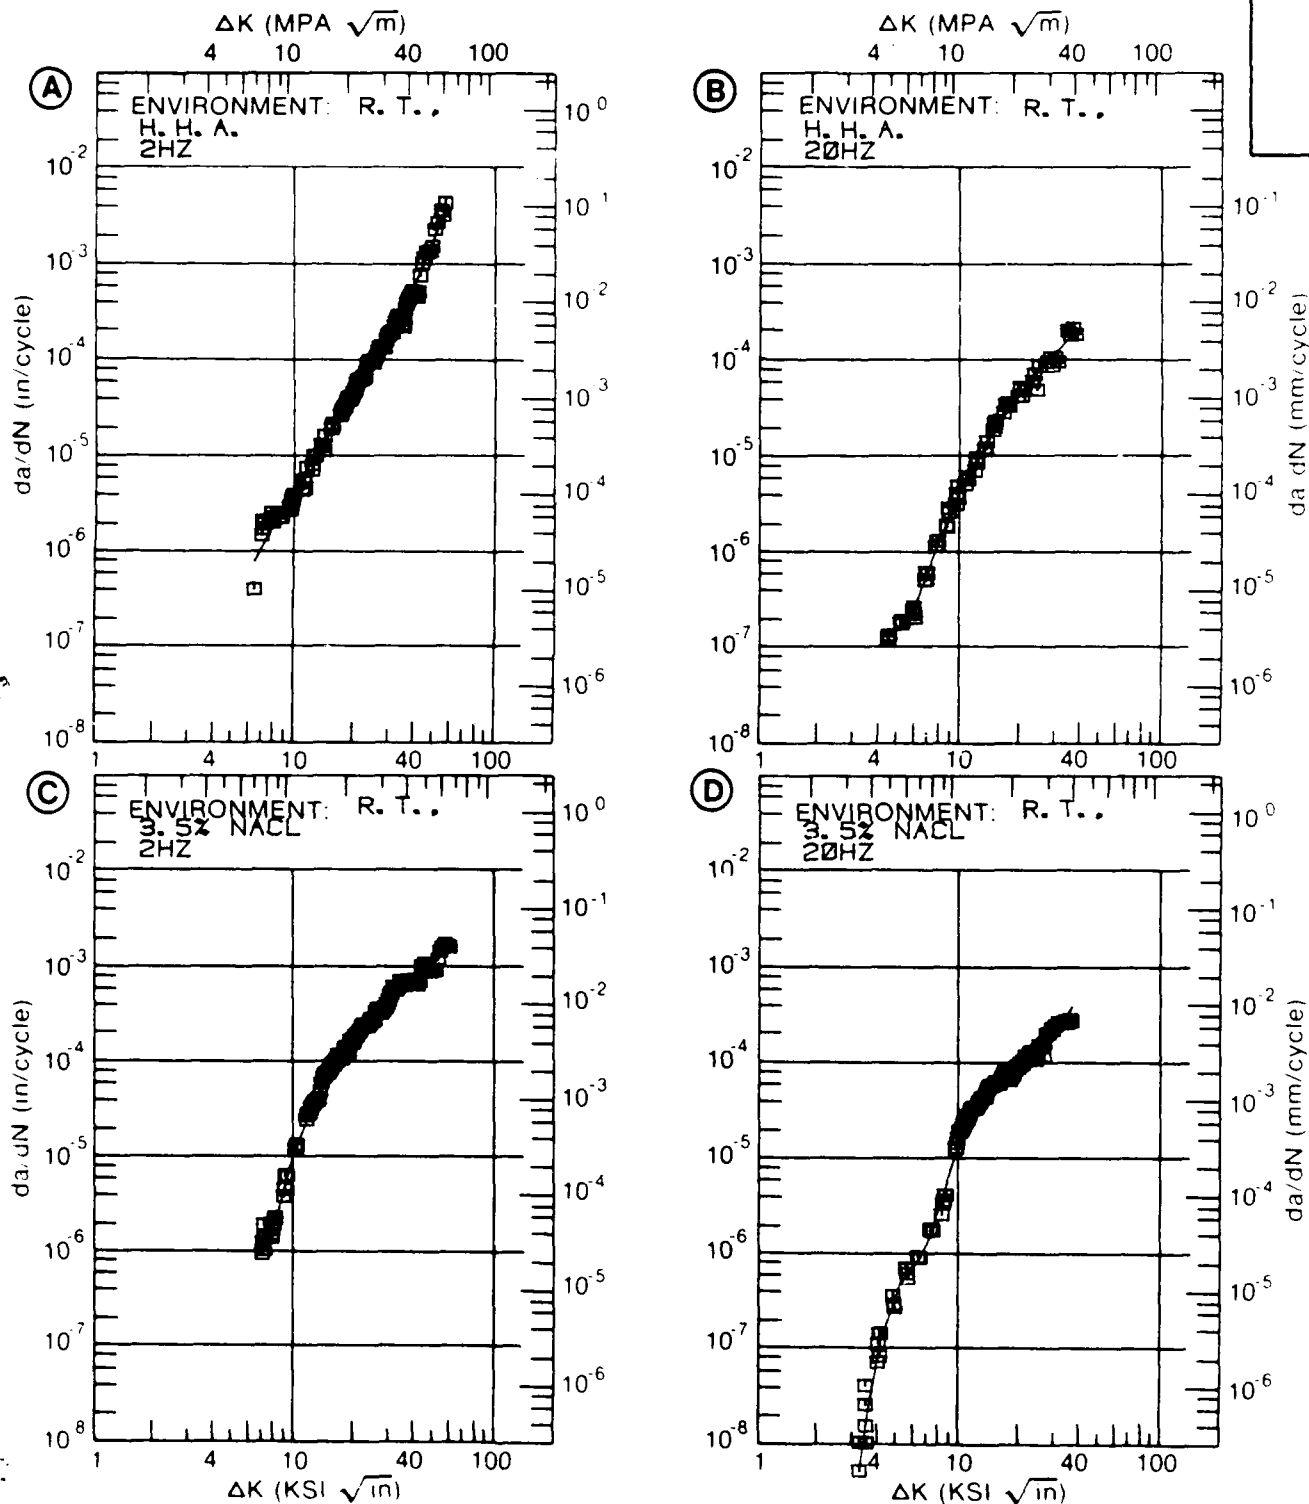


Figure 8.7.3.54

TABLE 8.7.3.55

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.55 INDICATING EFFECT
OF STRESS RATIO

MATERIAL: ALUMINUM 7050
CONDITION: T76511
ENVIRONMENT: R T , L. H. A.

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		R=+0.46			
DELTA K MIN	A: 6.63	2.12			
	B:				
	C:				
	D:				
	7.00	2.71			
	8.00	4.63			
	9.00	6.98			
	10.00	9.90			
	13.00	26.1			
DELTA K MAX	A: 15.21	56.7			
	B:				
	C:				
	D:				

ROOT MEAN SQUARE 5.30
PERCENT ERROR

LIFE 0.0-0.5
PREDICTION 0.5-0.8
RATIO 0.8-1.25 1
SUMMARY 1 25-2.0
(NP/NA) >2.0

CONDITION/HT: T76511
 FORM: 1.16" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 FREQUENCY: 18.30 HZ
 ENVIRONMENT: R. T., L. H. A.

YIELD STRENGTH: 76.4 KSI
 ULT. STRENGTH: 83.6 KSI
 SPECIMEN THK: 1.007"
 SPECIMEN WIDTH: 3.100"
 REFERENCES: AL004

ALUM. ALLOY
7050

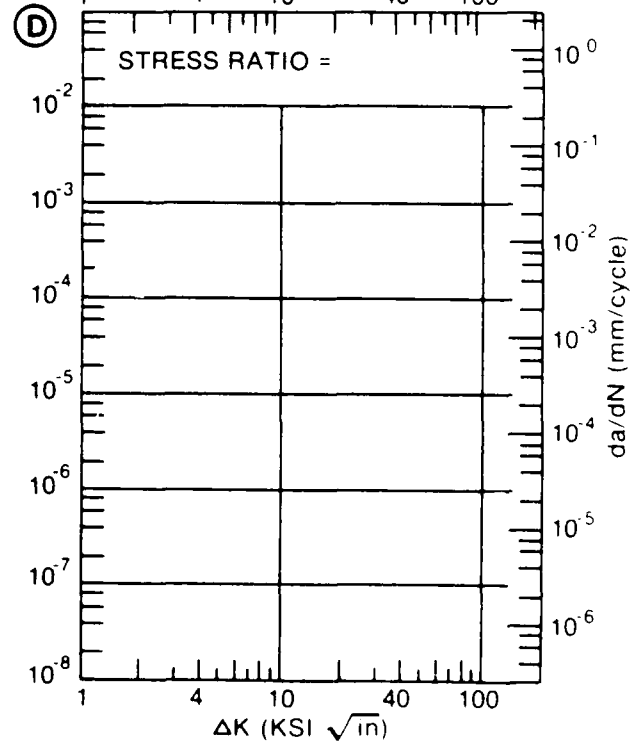
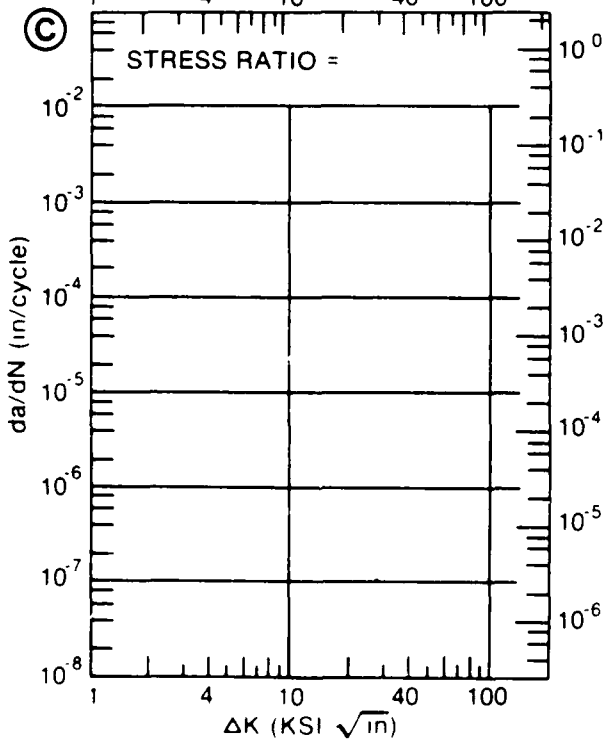
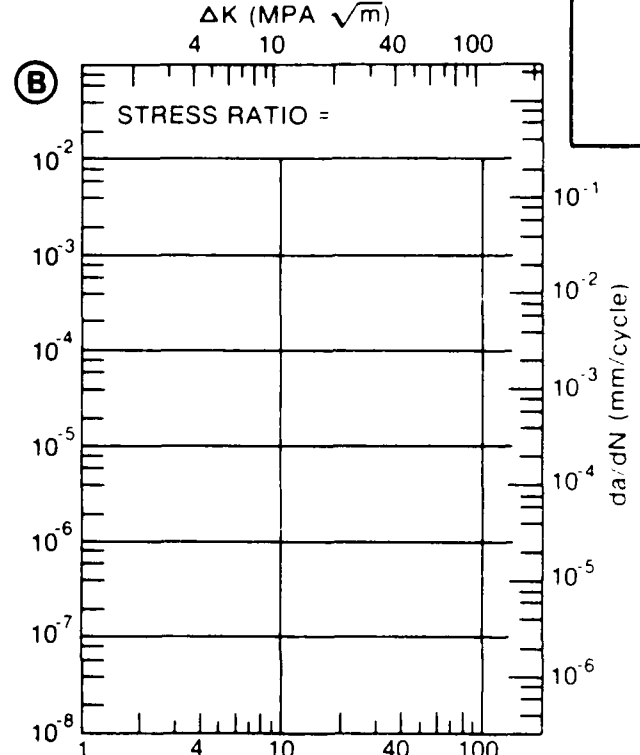
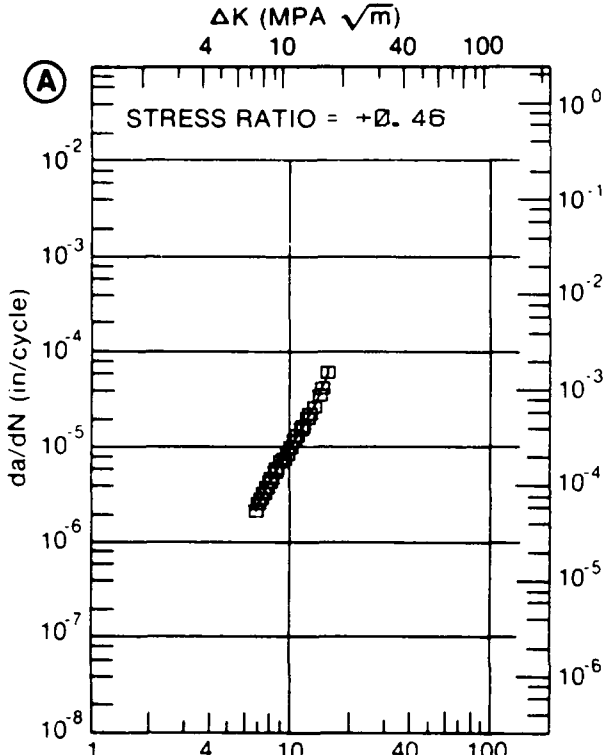


Figure 8.7.3.55

TABLE 8.7.3.56

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTORDATA ASSOCIATED WITH FIGURE 8.7.3.56 INDICATING EFFECT
OF ENVIRONMENTMATERIAL: ALUMINUM 7050
CONDITION: T76511

DELTA K (KSI*IN**1/2)	DA/DN (10**-6 IN./CYCLE)			
	A	B	C	D
	E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 4.53 B: 4.95 C: 4.52 D:	.361	.720	1.55
	5.00 6.00 7.00 8.00 9.00 10.00 13.00 16.00	.419 .626 .988 1.58 2.52 3.95	.794 2.83 5.29 8.10 11.4 15.4 38.4 81.1	2.56 7.06 11.7 15.7 19.3 23.5 47.5
DELTA K MAX	A: 11.55 B: 17.46 C: 15.13 D:	7.62	83.7	70.2
ROOT MEAN SQUARE PERCENT ERROR		9.30	15.98	12.58

LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	3	2
---------------------------------------	--	---	---	---

CONDITION/HT: T76511
 FORM: 1.16" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 19.30 HZ

YIELD STRENGTH: 76.4 KSI
 ULT. STRENGTH: 83.6 KSI
 SPECIMEN THK: 1.000- 1.007"
 SPECIMEN WIDTH: 3.100- 3.801"
 REFERENCES: AL004

ALUM. ALLOY
7050

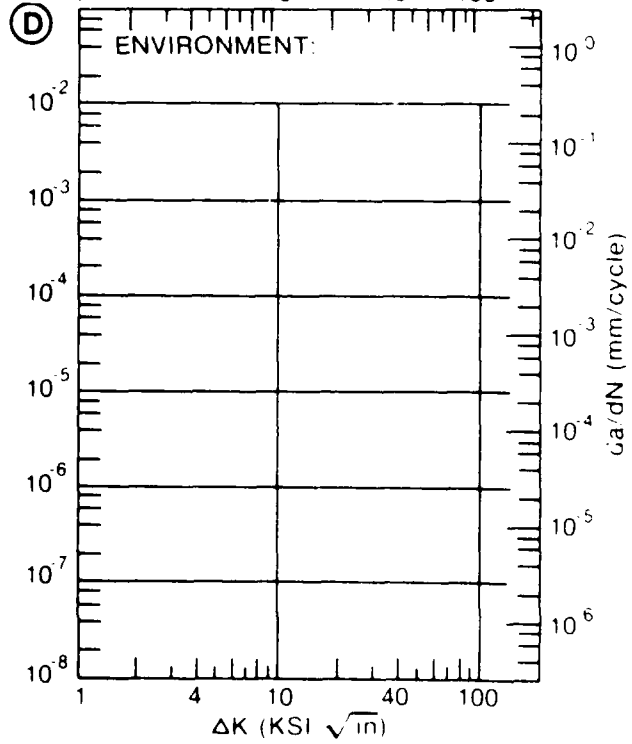
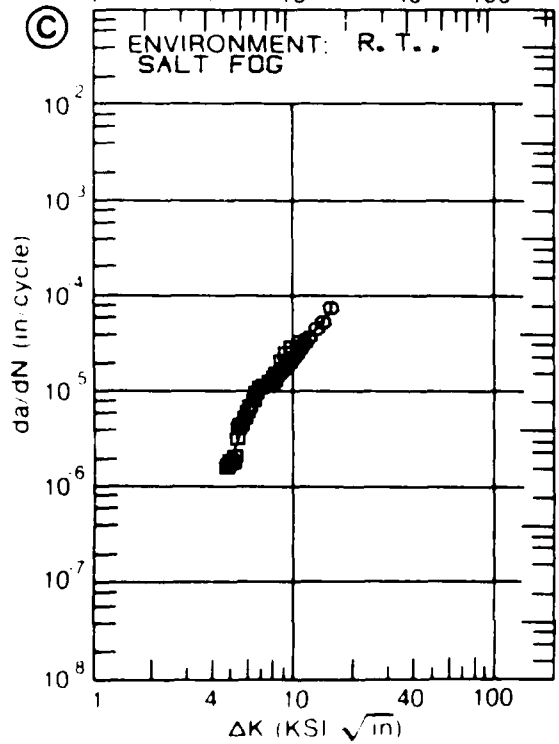
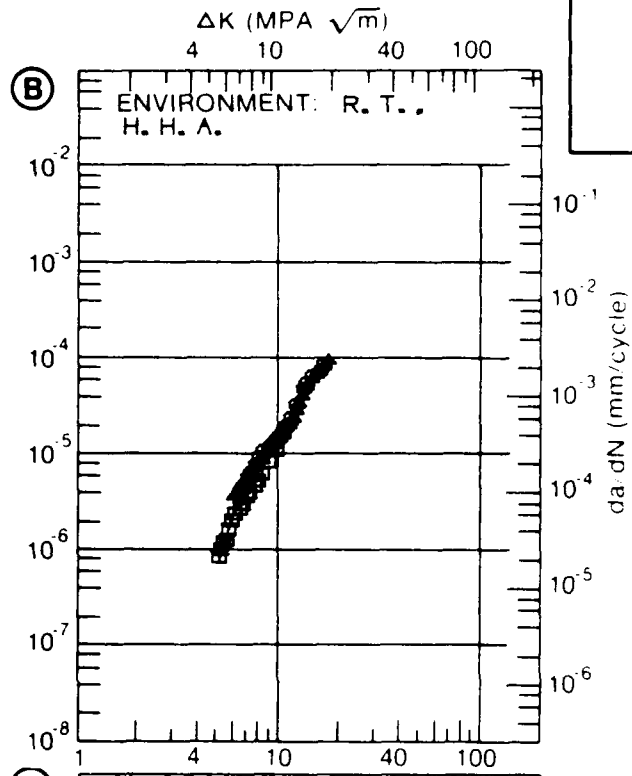
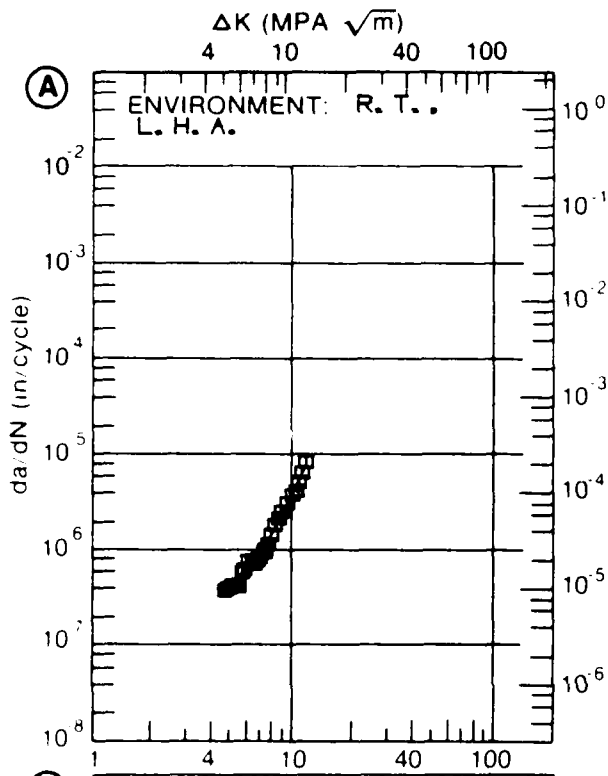


Figure 8.7.3.16

TABLE 8.7.3.57

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.57 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T76511					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K	A: 3.86	.323			
MIN	B: 6.00		5.43		
	C: 5.91			7.43	
	D:				
	4.00	.323			
	5.00	.810			
	6.00	1.76		7.66	
	7.00	2.71	8.50	10.7	
	8.00	3.68	12.0	14.8	
	9.00	4.87	16.0	20.0	
	10.00	6.38	20.5	26.7	
	13.00	14.4	39.2	50.8	
	16.00	35.5	71.5		
DELTA K	A: 18.47	93.4			
MAX	B: 17.14		89.7		
	C: 14.15			53.6	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		17.60	6.16	7.68	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5				
	0.5-0.8				
	0.8-1.25	2	1	1	
	1.25-2.0				
	>2.0				

CONDITION/HT: T76511
 FORM: 1.16" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: T-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 74.4 KSI
 ULT. STRENGTH: 82.5 KSI
 SPECIMEN THK: 0.999- 1.000"
 SPECIMEN WIDTH: 3.801"
 REFERENCES: AL004

ALUM. ALLOY
7050

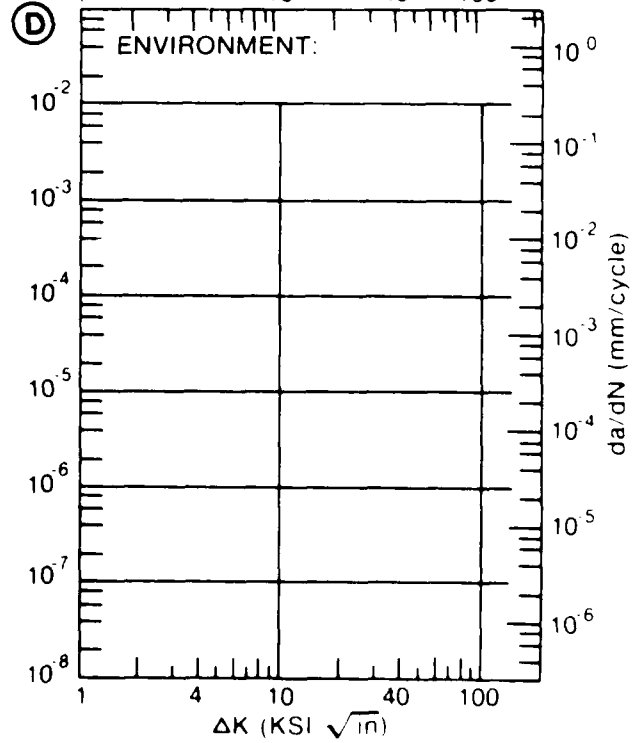
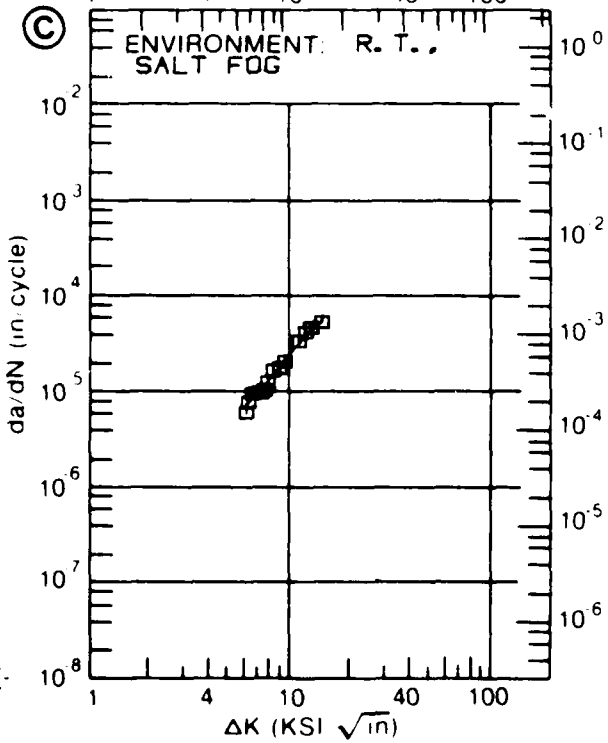
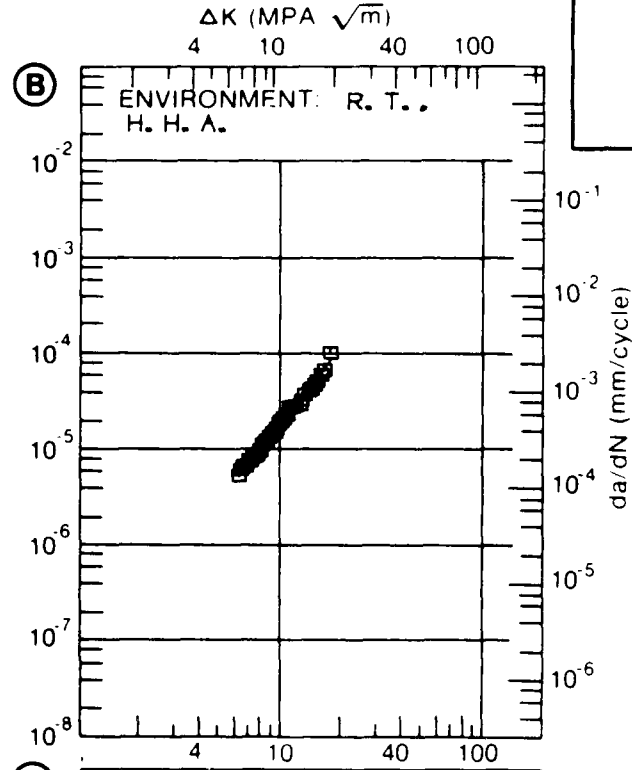
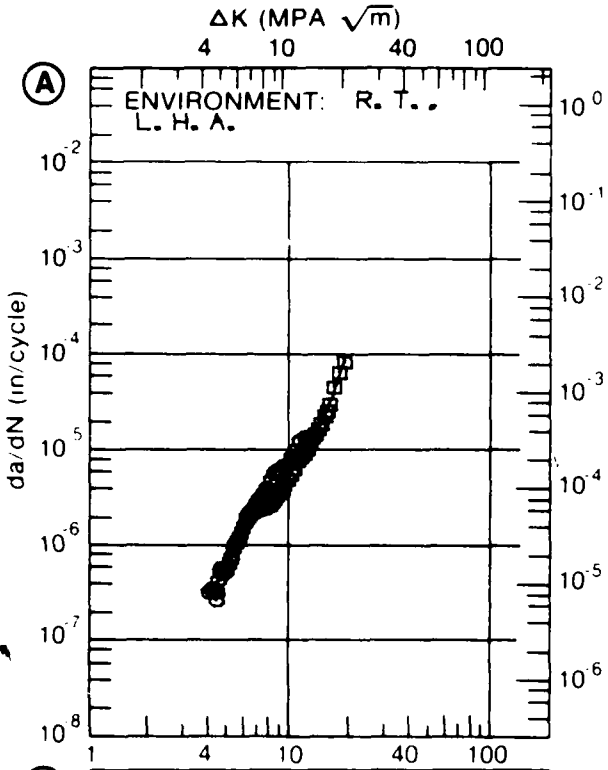


Figure 8.7.3.57

TABLE 8.7.3.58

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.58 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T76511					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K	A: 5.78	1.06			
MIN	B: 5.91		4.95		
	C: 7.98			8.09	
	D:				
	6.00	1.17	5.23		
	7.00	1.73	8.19		
	8.00	2.31	10.7	8.17	
	9.00	2.89	13.4	12.6	
	10.00	3.45	16.8	17.1	
	13.00	4.90			
	16.00	5.97			
DELTA K	A: 18.83	6.69			
MAX	B: 10.86		21.2		
	C: 12.68			26.1	
	D:				
ROOT MEAN SQUARE		10.06	5.74	2.40	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	2	1	1	

CONDITION/HT: T76511
 FORM: 5.00" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 82.3- 82.6 KSI
 ULT. STRENGTH: 87.6 KSI
 SPECIMEN THK: 0.999- 1.003"
 SPECIMEN WIDTH: 3.100- 3.801"
 REFERENCES: AL004

ALUM.
 ALLOY

7050

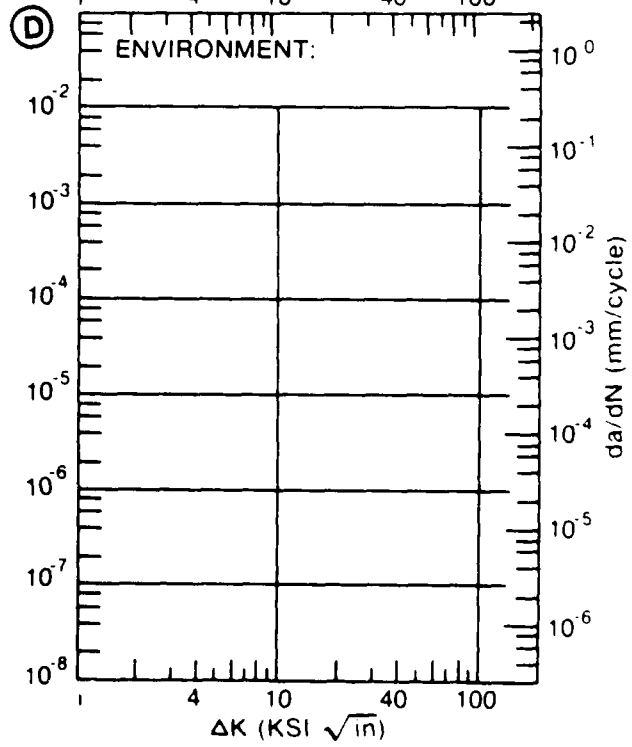
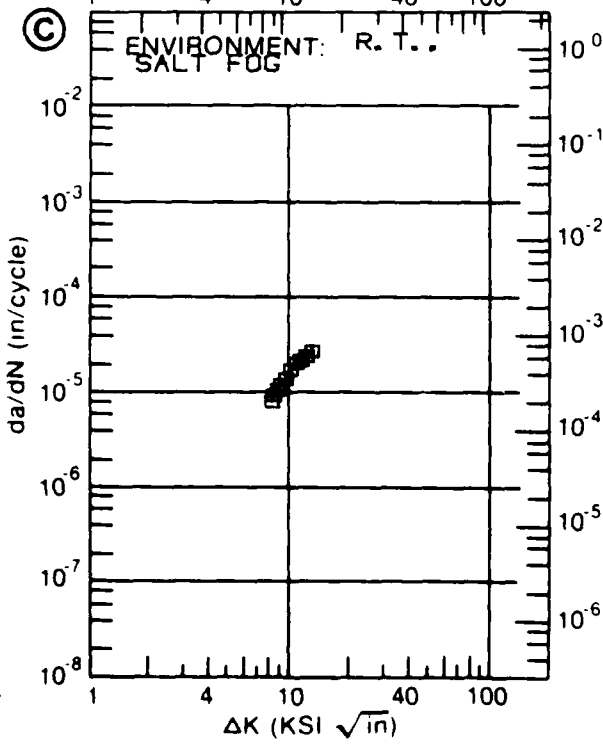
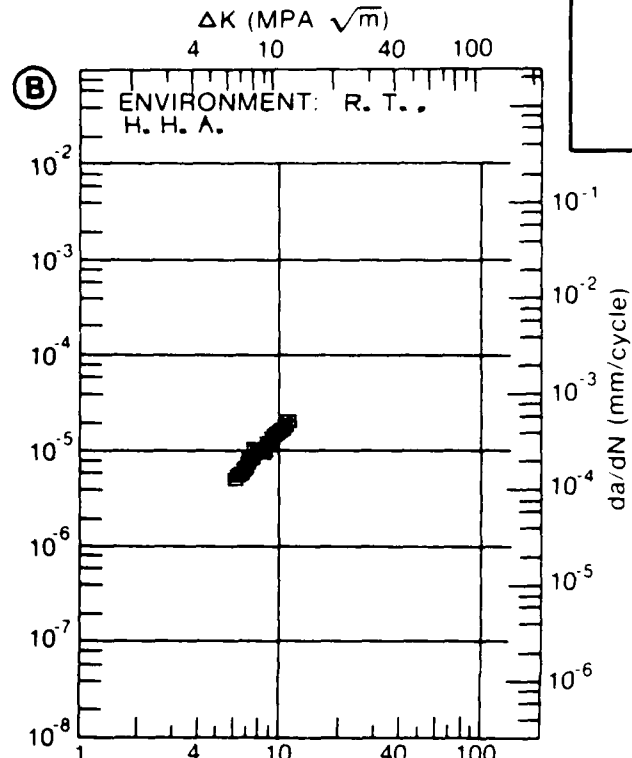
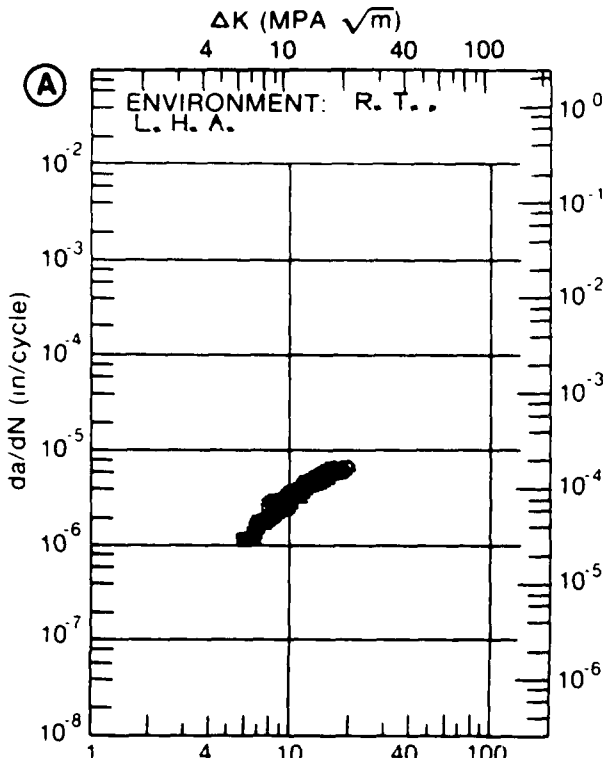


Figure 8.7.3.58

TABLE 8.7.3.59

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.7.3.59 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050			
CONDITION: T76511					
DELTA K (KSI*IN**1/2)		DA/DN (10**-6 IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.82	1.43			
	B: 3.89		1.05		
	C: 5.89			5.92	
	D: 4.00		1.01		
	5.00		1.71		
	6.00	1.53	4.91	6.82	
	7.00	2.38	11.9	14.9	
	8.00	4.68	23.4	22.4	
	9.00	12.4	41.0	35.8	
	10.00	43.9	121.	73.8	
DELTA K MAX	A: 10.02	45.2			
	B: 10.01		124.		
	C: 10.31			98.8	
	D:				
ROOT MEAN SQUARE		9.65	19.59	12.07	
PERCENT ERROR					
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	2	1	

CONDITION/HT: T76511
 FORM: 5.00" TH EXTRUSION
 SPECIMEN TYPE: CT
 ORIENTATION: S-L
 STRESS RATIO: +0.33
 FREQUENCY: 18.30 HZ

YIELD STRENGTH: 70.3- 82.3 KSI
 ULT. STRENGTH: 76.5- 87.6 KSI
 SPECIMEN THK: 0.958- 1.006"
 SPECIMEN WIDTH: 3.800- 3.801"
 REFERENCES: AL004

ALUM.
 ALLOY
 7050

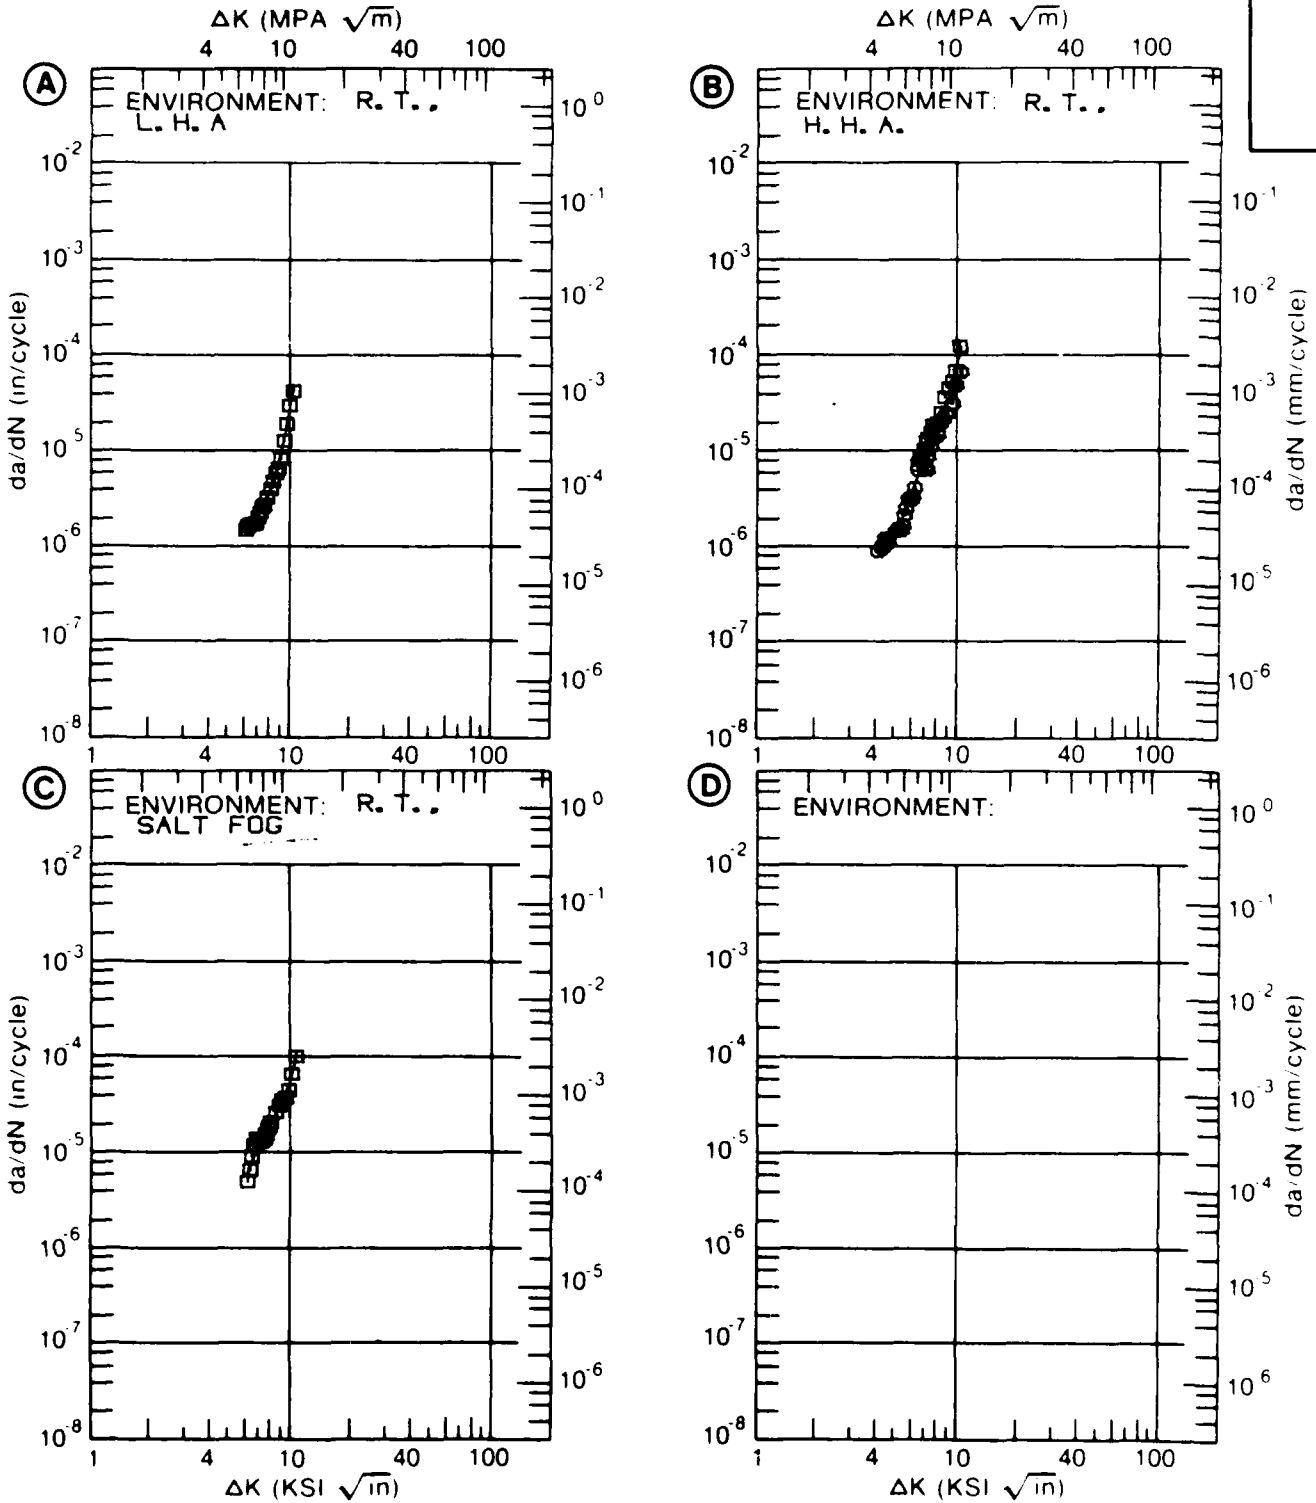


Figure 8.7.3.59

TABLE 8.7.3.60

CONDITION	ALUMINUM		TEST SPEC YIELD STR (KSI)	ENVIRONMENT	SPECIMEN		CRACK		K (ISCC)	MEAN	STAN DEV	TEST TIME (MIN)	DATE REFER
	PRODUCT FORM	THICK (IN)			THICK (IN)	DESIGN (IN)	LENGTH (IN)	K (ISCC)					
T736	F	0.25	R.T.	L-T	61.4	3.5	PCT NACL	DCB	31.10	28.20*			1973 86212
T736	F	0.25	R.T.	T-L	62.4	3.5	PCT NACL	DCB	28.10	24.50*			1973 86212
T73651	P	4.00	R.T.	T-L	67.2		DIST WATER	TDCB	30.00	29.10			1972 84362
T73651	P	4.00	R.T.	T-L	66.0		S.T.W.	DCB	43.00	27.50			133680 1976 R1006
T73651	P	4.00	R.T.	T-L	67.2	3.5	PCT NACL	TDCB	30.00	29.10			133680 1976 R1006
T7651	P	1.25	R.T.	L-T	73.8		JP-4 FUEL	WDL *	1.086	22.40			>95040 1977 MA005
T7651	P	1.25	R.T.	L-T	73.8		SEA WATER	WDL *	1.092	22.60			>95040 1977 MA005
T7651	P	1.25	R.T.	T-L	77.0		JP-4 FUEL	WDL *	1.131	22.00			>95040 1977 MA005
T7651	P	1.25	R.T.	T-L	77.0		SEA WATER	WDL *	1.131	21.90			>95040 1977 MA005
T7651	P	1.25	R.T.	T-L	77.0		SIM.	WDL *	1.156	22.50			>95040 1977 MA005
T7651	P	1.25	R.T.	T-L	77.0		SIM.	WDL *	1.101	22.30			>95040 1977 MA005
T7651	P	1.25	R.T.	T-L	77.0		SIM.	WDL *	1.091	22.30			>95040 1977 MA005

*NOTE-DATA WHICH DO NOT MEET MINIMUM SPECIMEN THICKNESS REQUIREMENTS OF 2.5(KISCC/TYS)SQUARED

TABLE 8.8.1.1

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR
ALUMINUM 7050 (ALCLAD)

TEST CONDITIONS		ENVIRONMENT	L H A A T R T	FATIGUE CRACK GROWTH RATES (MICRIN/CYCLE)		
SPECIMEN ORIENTATION	T-1			DELTA K LEVELS (KSI SQRT(IN))	5	10
CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	50	100	100
T76	SHEET	0 00	13 30	4 66		
T76	SHEET	0 33	13 30	6 90		
T76	SHEET	0 67	13 30	1 70	2 3 5	

TABLE 8.8.1.2

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050 (ALCLAD)

TEST CONDITIONS

ORIENTATION T T

ENVIRONMENT H H A
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2	5	10	20	50	100
176	SHEET	0.00	13.30							8.03
176	SHEET	0.33	13.30			1.51	13.7			
176	SHEET	0.67	13.30			2.47	27.7			

TABLE 8.8.1.3

FATIGUE CRACK GROWTH RATE AT DEFINED LEVELS OF THE STRESS-INTENSITY FACTOR

ALUMINUM 7050 (ALCLAD)

TEST CONDITIONS

SPECIMEN ORIENTATION T I

ENVIRONMENT SALT FOG
A T R T

CONDITION/HT	PRODUCT FORM	STRESS RATIO	FREQ (HZ)	DELTA K LEVELS (KSI SQRT(IN))	FATIGUE CRACK GROWTH RATES (MICRO IN/CYCLE)					
					2	5	10	20	50	100
176	SHEET	0 00	13 30							11 6
176	SHEET	0 33	13 30							21 4
176	SHEET	0 47	13 30					4 82	39 0	

TABLE 8.8.2.1

CONDITION	ALUMINUM		7050 (ALCLAD)		K(C)		CRACK LENGTH CROSS STRESS				K(APP) STAN		K(C) STAN				
	--PRODUCT-- FORM	THICK (IN)	TEST TEMP (F)	SPEC OR	YIELD STR (KSI)	--SPECIMEN--		INIT (IN)	FINAL (IN)	ONSET (KSI)	MAX (KSI)	K(APP) (KSI*SQRT IN)	MEAN (KSI*SQRT IN)	STAN DEV	K(C) MEAN (KSI*SQRT IN)	STAN DEV	DATE REFER
						WIDTH (IN)	THICK (IN)										
T76	S	0.06	R T	L-T	67.2	8.130	0.062	2.670	4.090	---	37.50	82.50*	113.50*	---	1982	LG002	
		0.06			67.2	8.130	0.062	2.670	3.920	---	37.40	82.20*	108.70*	---	1982	LG002	
		0.06			67.2	8.130	0.063	2.670	3.960	---	37.90	83.40*	101.90*	---	1982	LG002	
T76	S	0.06	R T	L-T	67.2	12.030	0.062	3.990	5.410	---	33.70	90.70	112.70*	---	1982	LG002	
		0.06			67.2	12.050	0.062	4.030	5.640	---	35.30	95.70	93.2/ 3.5	122.10*	---	1982	LG002
T76	S	0.06	R T	L-T	67.2	20.020	0.062	6.650	8.070	---	27.40	95.00	108.70	---	1982	LG002	
		0.06			67.2	20.070	0.063	6.560	8.730	---	28.40	97.60	96.3/ 1.8	119.40	114.1/ 7.6	1982	LG002
T76	S	0.09	R T	L-T	66.9	8.120	0.087	2.700	3.860	---	35.10	77.60	100.80*	---	1982	LG002	
		0.09			66.9	8.120	0.088	2.680	3.860	---	34.30	75.40	98.50*	---	1982	LG002	
		0.09			66.9	8.120	0.088	2.660	4.020	---	34.80	76.30	76.4/ 1.1	103.70*	---	1982	LG002
T76	S	0.09	R T	L-T	66.9	12.100	0.087	3.990	5.590	---	31.70	85.30	108.80*	---	1982	LG002	
		0.09			66.9	12.110	0.088	4.030	6.090	---	31.60	85.60	116.80*	---	1982	LG002	
		0.09			66.9	12.120	0.088	3.980	5.850	---	31.30	83.90	84.9/ 0.9	111.50*	---	1982	LG002
T76	S	0.09	R T	L-T	66.9	20.140	0.088	6.600	10.030	---	28.80	99.50	136.00*	---	1982	LG002	
		0.09			66.9	20.170	0.088	6.650	9.760	---	30.50	105.70	102.6/ 4.4	140.40*	---	1982	LG002

*NOTE- NET SECTION STRESS EXCEEDS 80% OF YIELD STRENGTH. VALUE NOT INCLUDED IN MEAN OR STD. DEV

TABLE 8.8.3.1

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.8.3.1 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL ALUMINUM
CONDITION T76

7050 (ALCLAD)

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.02	.763			
	B: 4.99		1.50		
	C: 5.11			2.27	
	D:				
	5.00		1.51		
	6.00	1.77	2.76	4.74	
	7.00	2.91	4.55	8.28	
	8.00	4.05	6.93	12.3	
	9.00	5.31	9.97	16.7	
	10.00	6.90	13.7	21.4	
	13.00	17.6	29.4	39.3	
DELTA K MAX	A: 14.99	39.6			
	B: 14.43		39.2		
	C: 14.62			53.3	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		12.44	8.41	10.79	

LIFE PREDICTION RATIO SUMMARY (NP/NA)

2

2

2

0.0-0.5
0.5-0.8
0.8-1.25
1.25-2.0
>2.0

CONDITION/HT: T76
 FORM: Ø.03- Ø.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +Ø.33
 FREQUENCY: 13.3Ø HZ

YIELD STRENGTH: 65.1- 67.7 KSI
 ULT. STRENGTH: 74.2- 76.2 KSI
 SPECIMEN THK: Ø.024- Ø.122"
 SPECIMEN WIDTH: 3.999- 4.0Ø1"
 REFERENCES:ALØ12

ALUM.
 ALLOY
 7Ø5Ø
 (ALCLAD)

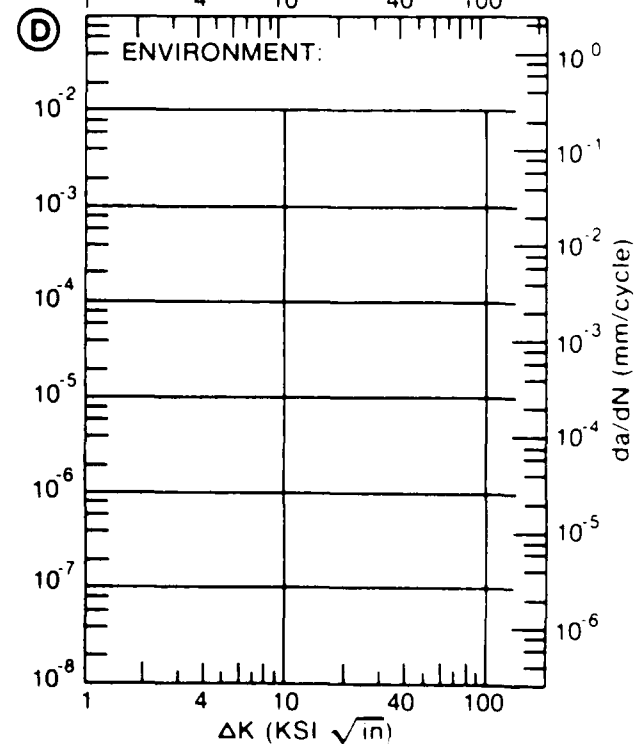
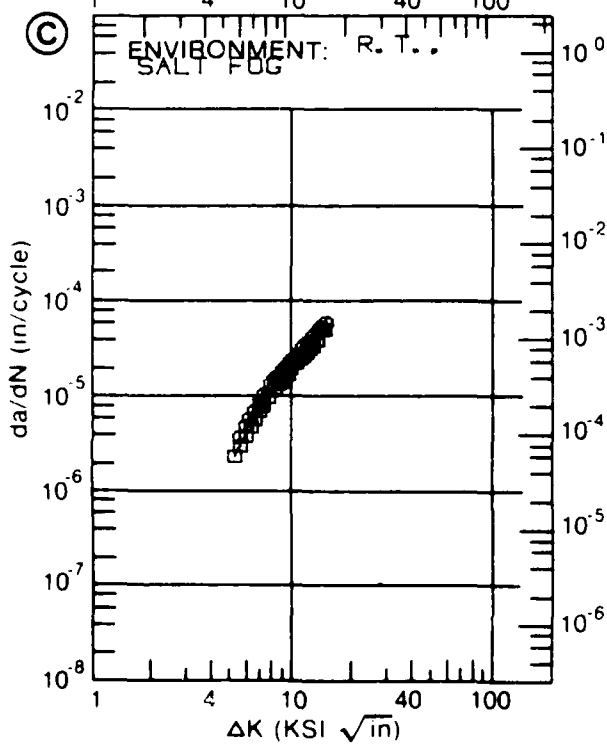
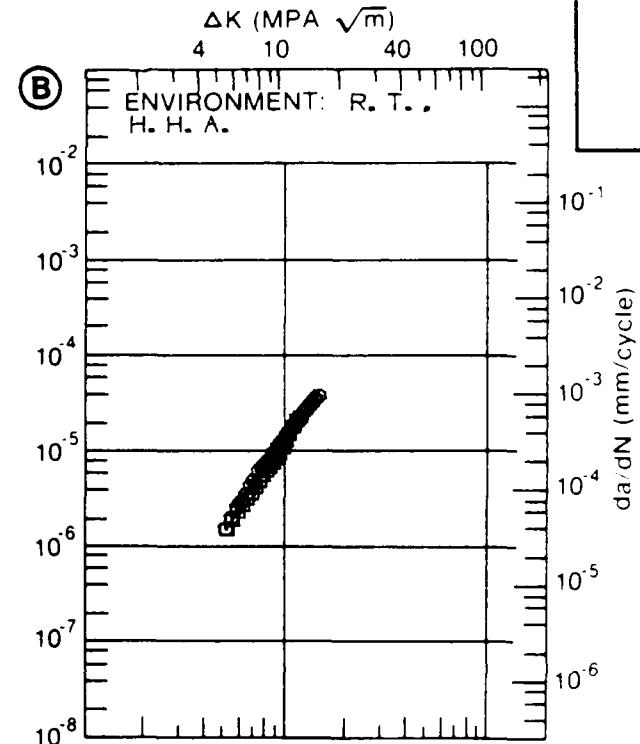
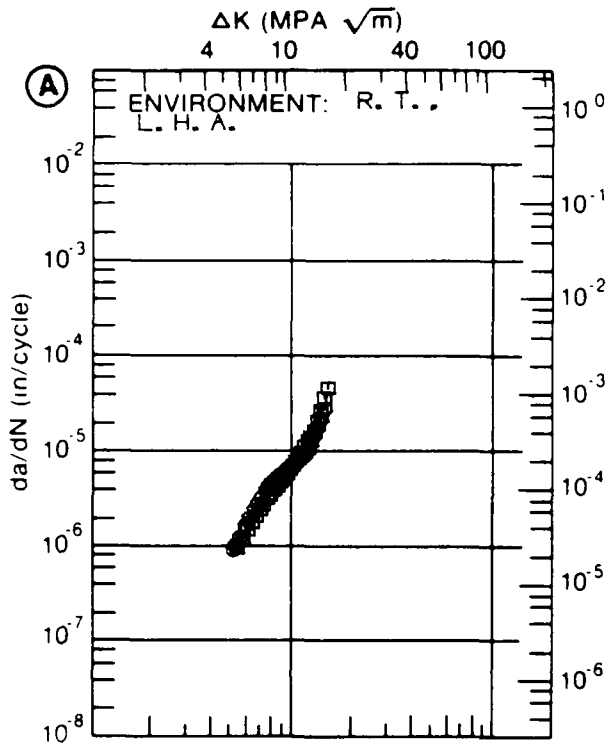


Figure 8.8.3.1

TABLE 8.8.3.2

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.8.3.2 INDICATING EFFECT
OF ENVIRONMENT

DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN./CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.07	.729			
	B: 5.08		1.51		
	C: 5.70			4.90	
	D:				
	6.00	1.69	2.85	5.92	
	7.00	3.06	4.82	10.0	
	8.00	4.63	7.33	15.2	
DELTA K MAX	9.00	6.35	10.4	21.3	
	10.00	8.19	14.0	28.1	
	13.00	15.3	29.4	51.6	
	16.00	27.4			
	A: 16.45	30.0			
	B: 14.28		38.5		
	C: 14.10			60.8	
D:					
ROOT MEAN SQUARE PERCENT ERROR		4.79	2.06	2.81	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1	

CONDITION/HT: T76
 FORM: Ø. 13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: L-T
 STRESS RATIO: +Ø. 33
 FREQUENCY: 13. 00 HZ

YIELD STRENGTH: 67. 3 KSI
 ULT. STRENGTH: 75. 2 KSI
 SPECIMEN THK: Ø. 121"
 SPECIMEN WIDTH: 4. 001"
 REFERENCES: ALØ12

ALUM.
 ALLOY
 7050
 (ALCLAD)

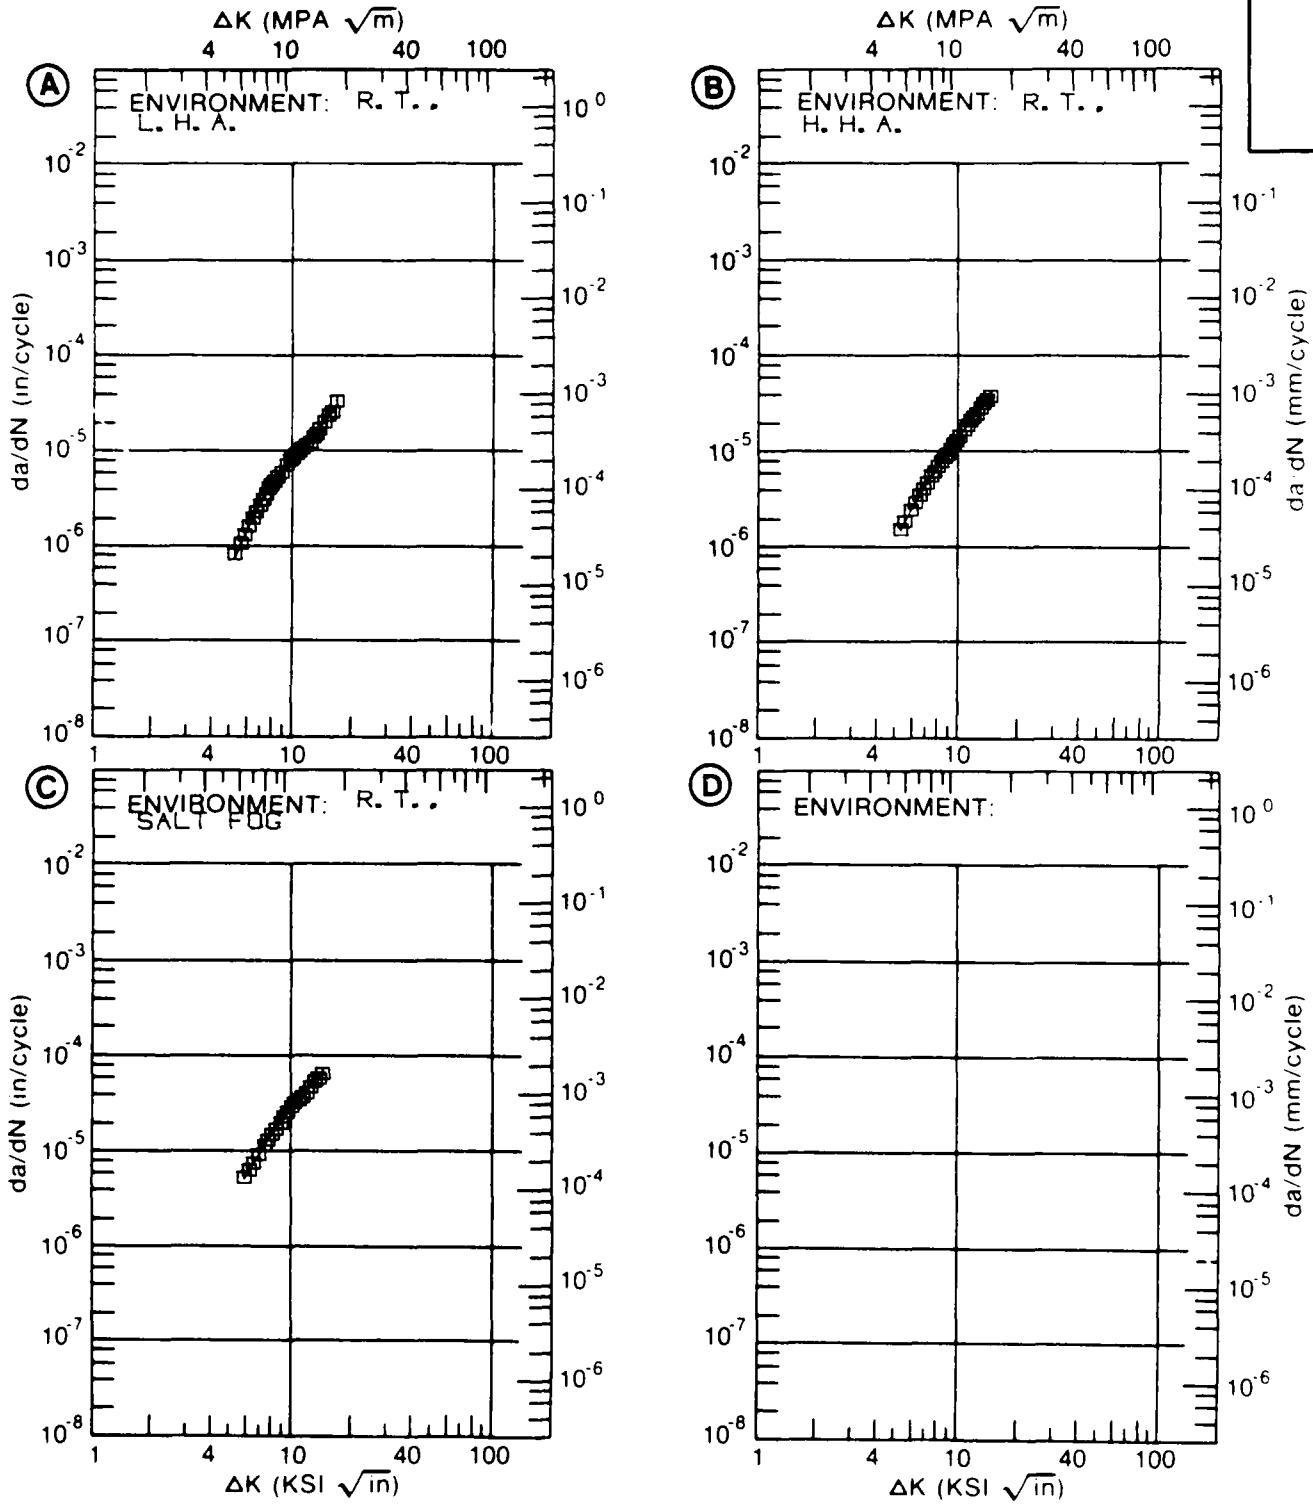


Figure 8.8.3.2

TABLE 8.8.3.3

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.8.3.3 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM CONDITION: T76		7050 (ALCLAD)			
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K MIN	A: 5.75	.541			
	B: 5.77		.944		
	C: 5.81			1.99	
	D:				
	6.00	.695	1.19	2.27	
	7.00	1.49	2.43	4.07	
	8.00	2.49	3.95	6.27	
	9.00	3.56	5.81	8.79	
	10.00	4.66	8.03	11.6	
	13.00	8.01	16.5	22.0	
	16.00	12.3	27.0	36.8	
DELTA K MAX	A: 16.45	13.1			
	B: 16.53		29.1		
	C: 16.50			39.9	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		5.27	3.32	4.58	
LIFE PREDICTION RATIO SUMMARY (NP/NA)	0.0-0.5 0.5-0.8 0.8-1.25 1.25-2.0 >2.0	1	1	1	

CONDITION/HT: T76
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.00
 FREQUENCY: 13.30 HZ

YIELD STRENGTH: 67.7 KSI
 ULT. STRENGTH: 76.2 KSI
 SPECIMEN THK: 0.121"
 SPECIMEN WIDTH: 4.001- 4.002"
 REFERENCES: AL012

ALUM.
ALLOY

7050
(ALCLAD)

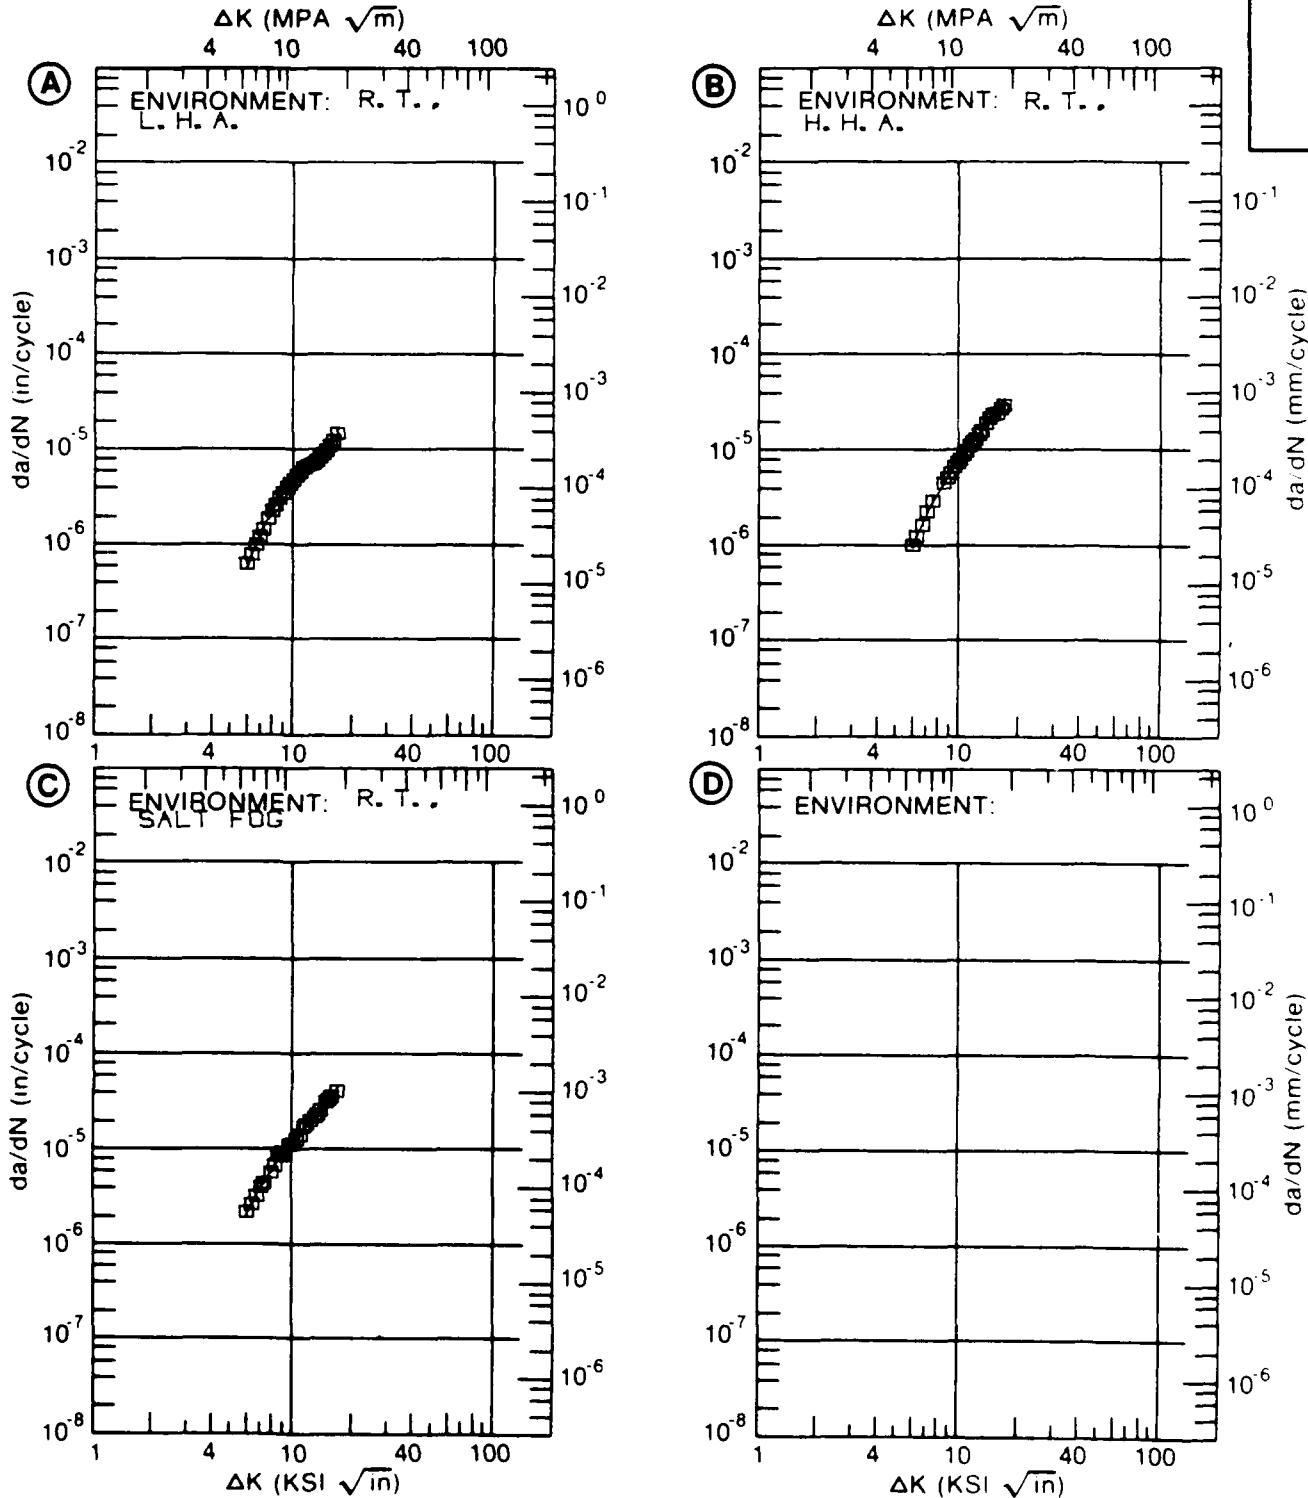


Figure 8.8.3.3

TABLE 8.8.3.4

FATIGUE CRACK GROWTH RATES AT DEFINED LEVELS
OF STRESS INTENSITY FACTOR

DATA ASSOCIATED WITH FIGURE 8.8.3.4 INDICATING EFFECT
OF ENVIRONMENT

MATERIAL: ALUMINUM		7050 (ALCLAD)			
CONDITION: T76					
DELTA K (KSI*IN**1/2)		DA/DN (10** ⁻⁶ IN. /CYCLE)			
		A	B	C	D
		E= R. T. L. H. A.	E= R. T. H. H. A.	E= R. T. SALT FOG	
DELTA K	A: 3.41	.410			
MIN	B: 3.56		.714		
	C: 3.51			1.06	
	D:				
	3.50	.453			
	4.00	.750	1.10	1.81	
	5.00	1.70	2.47	4.82	
	6.00	3.31	4.69	9.39	
	7.00	5.85	8.01	14.8	
	8.00	9.70	12.7	21.2	
	9.00	15.4	19.1	29.0	
	10.00	23.5	27.7	39.0	
DELTA K	A: 10.22	25.7			
MAX	B: 10.18		29.5		
	C: 10.50			45.2	
	D:				
ROOT MEAN SQUARE PERCENT ERROR		4.32	2.80	4.27	
LIFE	0.0-0.5				
PREDICTION	0.5-0.8				
RATIO	0.8-1.25	1	1	1	
SUMMARY	1.25-2.0				
(NP/NA)	>2.0				

CONDITION/HT: T76
 FORM: 0.13" TH SHEET
 SPECIMEN TYPE: CCP
 ORIENTATION: T-L
 STRESS RATIO: +0.67
 FREQUENCY: 13.30 HZ

YIELD STRENGTH: 67.7 KSI
 ULT. STRENGTH: 76.2 KSI
 SPECIMEN THK: 0.121- 0.122"
 SPECIMEN WIDTH: 4.001"
 REFERENCES: AL012

ALUM.
 ALLOY
 7050
 (ALCLAD)

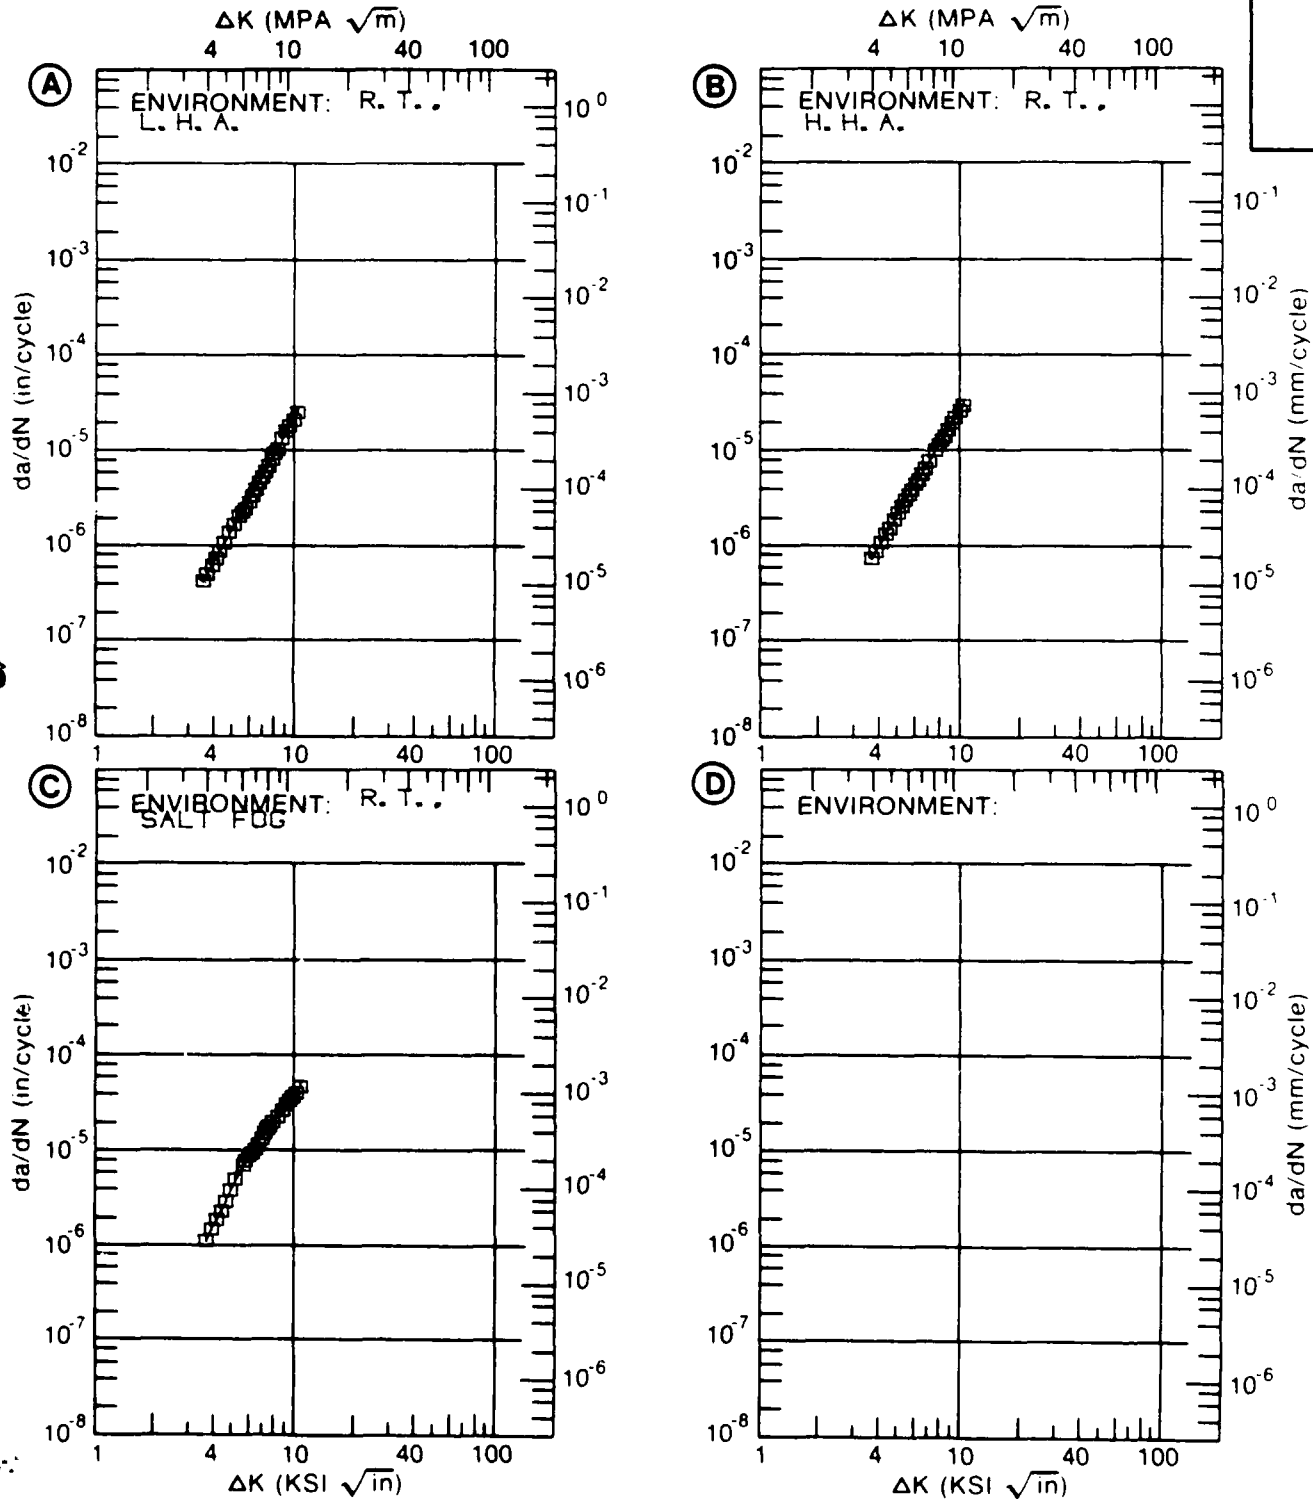


Figure 8.8.3.4