

AD-A151 446

A SOLUBLE LINEAR SCHIFF-BASE COORDINATION POLYMER
CONTAINING EIGHT-COORDI. (U) MASSACHUSETTS UNIV AMHERST
DEPT OF CHEMISTRY R D ARCHER ET AL. FEB 85 TR-6
N00014-81-K-0611

1/1

UNCLASSIFIED


F/G 7/3

NL

END

FILMED

DTIC

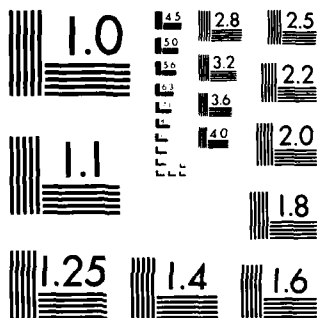

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

EMD 2

REPORT DOCUMENTATION PAGE

READ INSTRUCTIONS BEFORE COMPLETING FORM

1. REPORT NUMBER 6		2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) A Soluble Linear Schiff-Base Coordination Polymer Containing Eight-Coordinate Zirconium(IV)		5. TYPE OF REPORT & PERIOD COVERED Technical Report, Interim	
AUTHOR(s) Ronald D. Archer, Marvin L. Illingsworth, Denise N. Rau and Christopher J. Hardiman		6. PERFORMING ORG. REPORT NUMBER	
PERFORMING ORGANIZATION NAME AND ADDRESS Department of Chemistry University of Massachusetts Amherst, MA 01003		8. CONTRACT OR GRANT NUMBER(s) N00014-81-K0611	
CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Department of the Navy Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR056-773	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE February, 1985	
		13. NUMBER OF PAGES 31	
		15. SECURITY CLASS. (of this report) Unclassified	
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release, Distribution Unlimited		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) This document has been approved for public release and sale; its distribution is unlimited		DTIC ELECTRIC MAR 15 1985	
18. SUPPLEMENTARY NOTES Accepted for publication in <u>Macromolecules</u> , a journal published by the American Chemical Society.		E	
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) bridging ligands coordination polymer eight-coordinate chelate polymer film-forming metal chelate polymer gel permeation chromatography		Schiff-base coordination polymer, thermal stability, zirconium polymer. 49,000	
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The first soluble linear Schiff-base heavy metal coordination polymer has been synthesized via the condensation of 1,2,4,5-tetraaminobenzene and tetrakis-(salicylaldehydato)zirconium(IV) in dry dimethyl sulfoxide. The N,N',N'',N'''-tetrasalicylidene-1,2,4,5-tetraaminobenzeneatozirconium(IV) polymer has a number average molecular weight of up to 4.9×10^4 based on inherent viscosity, gel permeation chromatography, and elemental analysis. Spectral properties of this polymer indicate a structure analogous to the model compound, bis(N,N'-disalicylidene-1,2-phenylenediamino)zirconium(IV). Thermal characterization of ---			

AD-A151 446

DTIC FILE COPY

DD FORM 1 JAN 73 1473

85 03 06 005

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

OFFICE OF NAVAL RESEARCH

Contract N00014-81-K-0611

Task No. NR 056-773

TECHNICAL REPORT NO. 6

A SOLUBLE LINEAR SCHIFF-BASE COORDINATION POLYMER
CONTAINING EIGHT-COORDINATE ZIRCONIUM(IV)

by

Ronald D. Archer, Marvin L. Illingsworth,
Denise N. Rau and Christopher J. Hardiman

Prepared for Publication

in

Macromolecules

University of Massachusetts

Department of Chemistry

Amherst, MA 01003

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
PCIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

February 1985

Reproduction in whole or in part is permitted for
any purpose of the United States Government.

This document has been approved for public release
and sale; its distribution is unlimited.



A Soluble Linear Schiff-base Coordination Polymer Containing
Eight-coordinate Zirconium(IV)

RONALD D. ARCHER,* MARVIN L. ILLINGSWORTH,
DENISE N. RAU and CHRISTOPHER J. HARDIMAN

Department of Chemistry, University of Massachusetts, Amherst, MA 01003

ABSTRACT


The first soluble linear Schiff-base heavy metal coordination polymer has been synthesized via the condensation of 1,2,4,5-tetraaminobenzene and tetrakis(salicylaldehydato)zirconium(IV) in dry dimethyl sulfoxide. The N,N',N'',N'''-tetrasalicylidene-1,2,4,5-tetraaminobenzeneatozirconium(IV) polymer has a number average molecular weight of up to 4.9×10^4 based on inherent viscosity, gel permeation chromatography, and elemental analysis. Spectral properties of this polymer indicate a structure analogous to the model compound, bis(N,N'-disalicylidene-1,2-phenylenediamino)zirconium(IV). Thermal characterization of the polymer is also discussed.

INTRODUCTION


Linear metal chelate polymers with Schiff-base ligands in which the metal is a part of the polymer backbone¹⁻⁵ or is added to a polymeric Schiff-base⁵⁻¹⁰ are typically insoluble materials. The x-ray study of bis(N,N'-disalicylidene-1,2-phenylenediamino)zirconium(IV)¹¹ shows that two quadridentate Schiff-base ligands on zirconium(IV) are oriented such that a polymeric extension should be distorted from a strictly linear geometry which might cause intermolecular stacking and intractability, a serious problem in

the attempted polymerizations of divalent ions with Schiff-base (and other) bridging ligands.¹² Furthermore, the possibility of flexibility for nonrigid metal centers, even with conjugated organic bridging ligands, provided further incentive to use zirconium as the metal for synthesizing a tractable Schiff-base chelate polymer. Zirconium(IV) eight-coordinate chelates are typically nonrigid.¹³ The D_{2d} dodecahedron and the D_{4d} square antiprism, which are the two most common geometrical arrangements for eight ligand donor atoms around a central metal ion, are very similar in energy and normally possess a low energy barrier to interconversion; thus, nonrigid behavior is typical, even for chelates.

Zirconium(IV) is a labile metal ion; therefore, we have used a bis(quadridentate) delocalized chelating ligand, N,N',N'',N''' -tetrasalicylidene-1,2,4,5-tetraaminobenzene, H_4 tsb, 1, to retard the rate of ligand exchange in solution, to allow extensive polymer chain growth, and to provide good thermal stability.¹⁴ Such Schiff-base ligands are capable of sufficient nonplanarity for the interconversion between the dodecahedron and the antiprism.^{15,16} Thus, nonrigidity, suggested above, should still be possible.

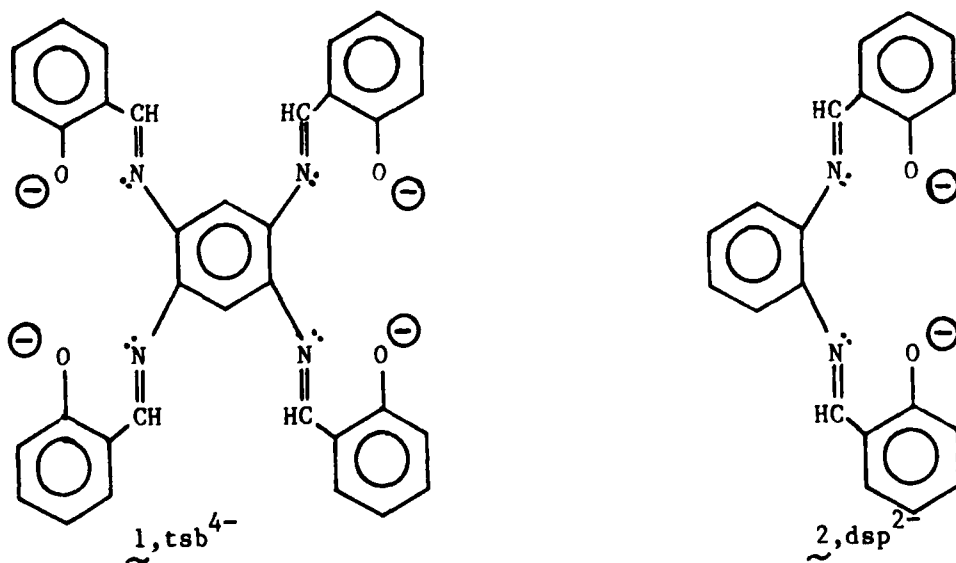

The soluble red coordination polymer has been obtained through the condensation of tetrakis(salicylaldehydato)zirconium(IV), $Zr(sal)_4$, with 1,2,4,5-tetraaminobenzene, TAB, analogous to the reaction between $Zr(sal)_4$ and *o*-phenylenediamine, which we reported previously.¹⁷ The low solubility of H_4tsb in ordinary solvents¹⁸ caused us to investigate this alternative to polymerization through normal ligand displacement reactions. This ligand-forming condensation reaction (1) proved successful.¹⁹

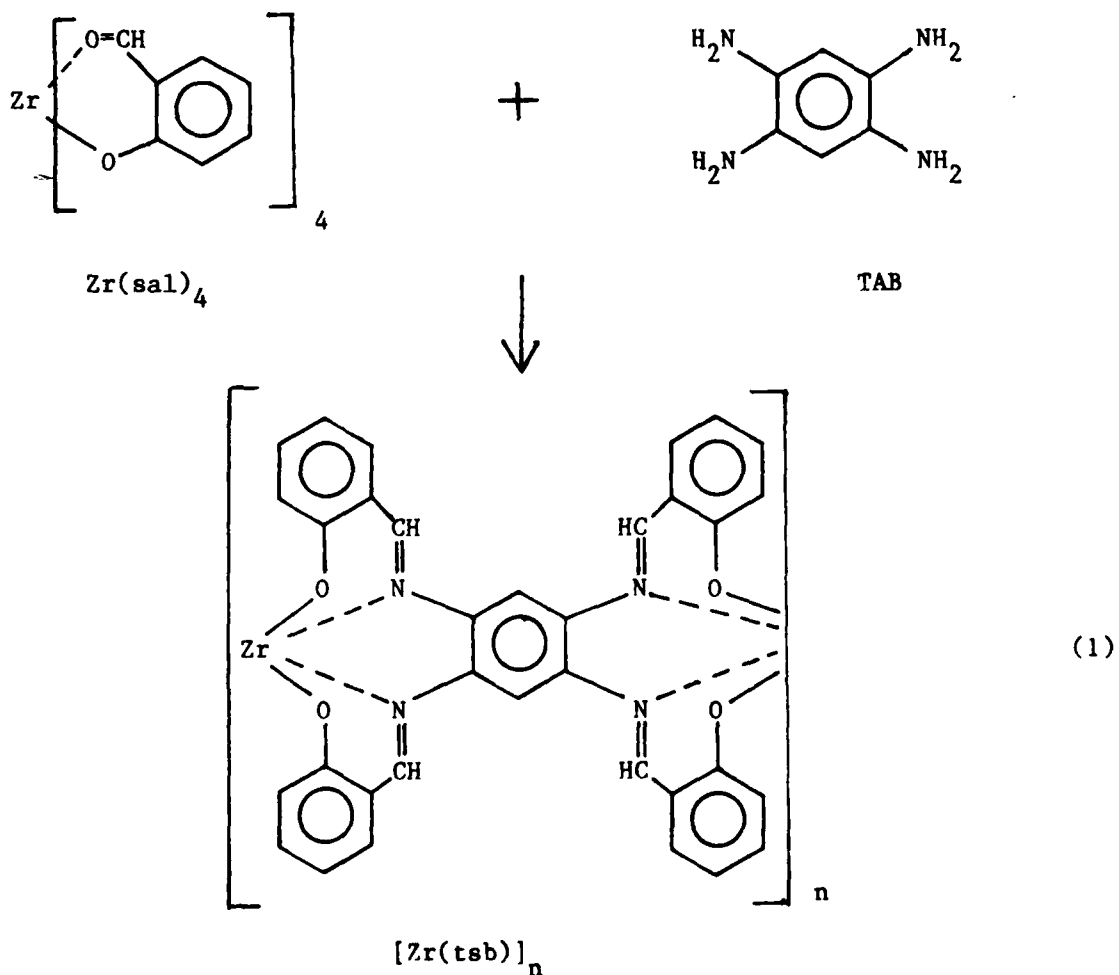

EXPERIMENTAL

Reagents

Reagent grade or equivalent solvents and chemicals were used. Prior to use, dimethyl sulfoxide (DMSO), γ -collidine, N-methylpyrrolidone (NMP), and mesitylene over calcium hydride were distilled under reduced pressure; methylene chloride over calcium hydride, and methanol and acetone over anhydrous calcium sulfate, were distilled at atmospheric pressure. A nitrogen atmosphere was used in the presence of free amines, with $Zr(sal)_4$, and during the polymerization reactions.

Tetrakis(salicylaldehydato)zirconium(IV)

$Zr(sal)_4$ was prepared as previously described¹⁷ and used promptly.

Poly[N,N',N'',N'''-tetrasalicylidene-1,2,4,5-tetraaminobenzeneatozirconium(IV)]

1,2,4,5-Tetraaminobenzene(TAB) tetrahydrochloride (Burdic and Jackson Laboratories) was dehydrohalogenated prior to use modifying the method of Dudgeon.²⁰ Twenty-five mL of oxygen-free water, 5.0 g (0.017 mol) $TAB \cdot 4HCl$ and a small amount of Norit A were mixed and heated to boiling under a nitrogen atmosphere. The hot mixture was suction-filtered into a dry-ice/acetone chilled flask. The clear and nearly colorless filtrate was then quickly transferred with stirring into 25 mL of ice-cold 15% aqueous NaOH solution and the free TAB instantly precipitated as white flakes. The mixture was filtered, ice-water washed, dried in vacuo, and weighed under nitrogen; yield, 1.43 g, 58%.

Then 0.816 g (5.92 mmol) TAB and 3.401 g (5.92 mmol) freshly prepared $\text{Zr}(\text{sal})_4$ were separately dissolved in 100 mL and 200 mL, respectively, of dry, deoxygenated DMSO under a nitrogen atmosphere. The pale tan tetraamine solution was added in one portion to the chartreuse-yellow $\text{Zr}(\text{sal})_4$ solution in a 500-mL flask. A deep red color developed immediately. With continued magnetic stirring, the DMSO-water azeotrope was slowly distilled under reduced pressure (41^o, 1.6 torr), leaving a red glassy solid, which was purified by dissolution in dry DMSO and precipitated with dry acetone.

Anal. Calcd. for $[\text{C}_{34}\text{H}_{22}\text{N}_4\text{O}_4\text{Zr}]_n$: C, 63.6; H, 3.43; N, 8.73; Zr, 14.2. Calcd. for 0.1 mol DMSO/Zr(tsb): C, 63.2; H, 3.5; N, 8.6; S, 0.5; Zr, 14.0. Found:²¹ C, 62.7; H, 3.8; N, 8.3; S, 0.8; Zr, 14.1.

Analysis of a sample prepared by in vacuo removal of DMSO solvent without the addition of acetone indicates about 1.7 moles DMSO per Zr unit and a Zr:4N ratio of 1.018. Calcd. for $\text{Zr}_{31}(\text{C}_{34}\text{H}_{22}\text{N}_4\text{O}_4)_{30}(\text{OH})_4 \cdot 53\text{C}_2\text{H}_6\text{SO}$: C, 57.4; H, 4.2; N, 7.1; S, 7.2; Zr, 12.0. Found: C, 57.1; H, 4.3; N, 7.0; S, 6.9; Zr, 11.6.

Bis(quadridentate) Schiff-base Ligands

Free TAB (1.20 g, 8.1 mmol) prepared as above was dissolved in 175 mL of dried deoxygenated DMSO, and a stoichiometric amount (3.95 g, 32.4 mmol) of salicylaldehyde was added. The resulting deep red solution was allowed to stand overnight under nitrogen. The copious red-orange precipitate which formed was filtered under a nitrogen stream, washed several times with dried acetone, and dried in vacuo.

Anal. Calcd. for $\text{C}_{34}\text{H}_{26}\text{N}_4\text{O}_4$: C, 73.6; H, 4.69; N, 10.1. Found: C, 72.7; H, 4.71; N, 9.7. Less than 0.15 mol DMSO gives excellent analytical agreement.

Derivatives of H₄tsb were prepared from the reaction of substituted salicylaldehydes with TAB using an excess of the aldehyde as a melt-solvent. For example, 0.8 g (6 mmol) of TAB and 20. g (130 mmol) of 3-methoxysalicylaldehyde were allowed to react for 20 min. at 50° Hot filtration of the excess molten aldehyde from the fine red precipitate was followed by trituration with methanol and ethyl ether to remove any final traces of the aldehyde. The precipitate was dried in vacuo at room temperature for 24 hr; yield, 1.8 g, 50%; mp. 261-2° (dec).

Anal. Calcd. for C₃₈H₃₄N₄O₈: C, 67.7; H, 5.04; N, 8.31. Found: C, 67.8; H, 4.99; N, 8.21.

Similarly, an analogous reaction between 1.0 g (7.2 mmol) of TAB and 20. g of molten 5-methoxysalicylaldehyde yielded 3.5 g, 70%, of a product with a mp., 280-280.5° (dec).

Anal. Calcd. for C₃₈H₃₄N₄O₈: C, 67.7; H, 5.04; N, 8.31. Found: C, 68.0; H, 5.19; N, 8.17.

Condensation of TAB with excess 5-bromosalicylaldehyde and 2-hydroxy-1-naphthaldehyde gave products of very low solubility in common organic solvents. They were not purified.

Physical Properties

The same instrumentation and physical methods of characterization cited previously¹⁷ were employed. In addition, thermal changes of polymer and model compounds were determined using a Dupont 900 Thermal Analyzer with a gas (nitrogen or air) flow of 0.2 liters per minute, a heating rate of 10° per minute, a sample size of 10 milligrams, and measured against aluminum chloride as a reference. Sample weight losses corresponding to these thermal changes

were measured on a Dupont 950 Thermogravimetric Analyzer using samples of similar size under identical conditions. Preliminary thermal decomposition pyrolysis was accomplished with a Chromalytics MP-3 Multi-purpose Thermal Analyzer. The products were trapped on glass beads using liquid nitrogen and separated with a Varian Aerograph Series 2700 gas chromatograph using Chromasorb 102 for the low boiling components and General Electric S.E. 30 on Chromasorb W support for the high boiling components.

Viscosity data in triplicate were collected in a Canon-Fenske Model No. 100-2873 viscometer or in an Ubbelohde Model No. 1, 2568 viscometer, equilibrated at $30.00 \pm 0.02^\circ$. The solvent was NMP.

A weight-loss experiment was conducted with a "furnace" consisting of a 6" test tube in a Wood's metal bath. A smaller 4" test tube served as the sample container. The sample container was preconditioned in the furnace for 24 hrs. prior to removal for rapid weighing, addition of 0.1 g polymer, reweighing, reheating, reweighing, etc. Weighings were to ± 0.2 mg.

Gel permeation chromatography of the zirconium polymer was conducted on a 10^3 Angstrom Ultrastyrigel column (Waters) with N-methyl-2-pyrrolidone (NMP) as the solvent.

RESULTS

Whereas H_4 tsb and its derivatives have very limited solubility, the reaction between $Zr(\text{sal})_4$ and TAB in DMSO produces an oligomer which is orders of magnitude more soluble. Solvent removal in vacuo or the addition of a miscible nonsolvent such as acetone is necessary to isolate a solid product.

Because the isopropyl derivative of H_4tsb had shown improved solubility over the unsubstituted compound,²² several derivatives were prepared to improve the solubility over the parent ligand while avoiding carbon-carbon single bonds. In dry donor solvents such as DMSO and γ -collidine, the 3- and 5-methoxy derivatives, which are reported here, show only modest solubility improvement relative to the parent compounds, while the slightly impure Schiff-base products obtained from condensation of 5-bromosalicylaldehyde or 2-hydroxy-1-naphthaldehyde with TAB show no solubility improvement at all.

These modest improvements are in sharp contrast to the polymer solubility improvement obtained in the chelate preparation between $Zr(sal)_4$ and TAB in DMSO. The soluble polymer solutions produce thin, light-diffracting films upon the slow evaporation of the DMSO solvent. [DMSO solutions of the free H_4tsb ligand produce crystalline particles.] The red glassy polymer appears to be amorphous since no x-ray diffraction pattern could be obtained, and under microscopic examination the polymer appears as red translucent irregular shaped particles with black striae.

The elemental analyses indicate 0.1 to 1.7 DMSO molecules per zirconium unit, the quantity of DMSO is dependant on the solvent mix. After considering the DMSO solvation, the excess of oxygen (by difference) is suggestive of OH end groups and/or water in the DMSO reaction product. Elemental analyses for N and Zr for a variety of samples indicate 1 ligand to 1 Zr within experimental error.

Inherent viscosities for $Zr(dsp)_2$ and the glassy $Zr(tsb)$ polymer samples were determined using Kraemer's approximation:²³

$$[\eta]_{inh} = (1/c) \ln (T_{solution}/T_{solvent})$$

where $[\eta]_{inh}$ = inherent viscosity
c = concentrations in g/dL
T = time in seconds

Samples of the polymer have been prepared which have inherent viscosity values of up to 0.18 dL/g in NMP as noted in Table I. The inherent viscosities of the polymer samples show negligible concentration dependence for series of dilute solutions so extrapolation to intrinsic viscosities is straight forward.

Gel permeation chromatography of the Zr(tsb) polymer samples in NMP yield number average molecular weights of as much as 49,000 relative to polystyrene standards as noted in Table I. The data for monomeric Zr(dsp)₂ is also included in Table I.

Comparing the Zr(tsb) polymer with the free ligand, the infrared frequency shifts are analogous to those observed for Zr(dsp)₂ relative to H₂dsp except for the persistence of O-H vibrations in the polymer. See Table II. The phenyl ring to oxygen stretch is shifted by 35 cm⁻¹ to higher frequencies in both the model chelate and the polymer relative to the respective neutral ligands. The imine C=N stretching vibration, by contrast, is almost unaffected, with frequency decreases of only a few wave numbers in both cases. The major difference is in the O-H stretching region, which shows no absorption in the model chelate, but persists with a peak and a shoulder in the polymer.²⁴

The zirconium polymer has an electronic spectrum in DMSO which is more complex and has lower energy transitions than those of the free ligand in the same solvent. Very similar behavior has been noted in the model Zr(dsp)₂ system,¹¹ and in other transition metal complexes of this ligand.^{18,22} See Table III.

Unlike monomeric $Zr(dsp)_2$ which has well behaved mass spectra¹¹ the polymer is not sufficiently volatile even at 275° to give a meaningful mass spectrum. Only a few very minor peaks are observed at mass to charge ratios of less than 300 m/e.

Thermal analysis of the polymer and the model compound by differential thermal analysis (DTA), thermogravimetric analysis (TGA), and pyrolysis-gas chromatography(P-GC) shows many analogous features as anticipated for compounds of similar structure. The DTA of the $[Zr(tsb)]_n$ polymer has a small endotherm which appears in the 130° - 190° range, probably due to loss of water and DMSO,²⁵ and thus is not observed in the DTA of the model compound. A noticeable weight loss near 160° is apparent in the polymer's TGA but not in the TGA of $Zr(dsp)_2$, which is consistent with this interpretation.

The next feature, ascending in temperature, is a small exotherm which occurs at 225 - 250° for the polymeric species in either nitrogen or air. While the DTA of freshly recrystallized, vacuum dried $Zr(dsp)_2$ is featureless at these temperatures, samples that have been allowed to stand at length in air display a nearly identical exotherm to the one described above in either nitrogen or air. In the TGA of one nine-month-old sample of $Zr(dsp)_2$, a corresponding two percent weight loss was observed; the analogous feature in the polymer TGA is masked by the DMSO evaporation.

In order to discern if a slow decomposition reaction occurs at room temperature or if a bond breaking and bond forming reaction takes place upon heating, infrared spectra of the fresh, aged, and heated (to 270°) $Zr(dsp)_2$ samples were recorded. The only difference displayed by the aged samples in comparison to the previously reported infrared spectrum of purified $Zr(dsp)_2$ ¹¹

CAPTION FOR FIGURE

Figure.--The anticipated structure for a portion of the $[\text{Zr}(\text{tsb})]_n$ polymer. The larger circles represent the Zr atoms and neither the ring below the plane of the molecule nor the H atoms are shown. The dodecahedral coordination about Zr is shown in Inset A. Note that organic portion of the ligand perpendicular to the plane of Inset A is skewed (cf., ref. 11) and provides two confirmation possibilities, the trans one shown for the chain and the cis one shown in Inset B, where the arrow points to the two nitrogens (one is below the one shown) with the changed configuration. Molecular models show that the configuration is possible, but the steric interactions cause us to favor the trans configuration shown at the left.

TABLE III. Electronic Spectral Results, cm^{-1} $\{\log \epsilon\}^{\text{a}}$

$[\text{Zr}(\text{tsb}) \cdot 1.7 \text{ DMSO}]_n$	$\text{H}_4(\text{tsb})$	$\text{H}_4[(3\text{-methoxy})_4\text{tsb}]$	$\text{H}_4[(5\text{-methoxy})\text{tsb}]$
39,000 sh ^b	36,700 {4.40} ^c	34,600 {4.45}	35,500 {4.36}
30,800 {4.45}	29,800 sh ^d 28,300 {4.55} ^c	29,200 sh 27,900 {4.62}	30,300 sh 27,000 {4.57}
26,500 w,sh 24,200 w,sh	25,600 {4.50} ^c	26,500 {4.61}	25,600 {4.61}
22,400 {4.59}	23,900 sh ^d	24,400 sh	23,500 sh
21,200 sh			

^aone cm matched cells, DMSO as solvent; ^b CH_2Cl_2 as solvent; ^cRef.18; ^dThis work.

TABLE II. Infrared Spectral Results for the New Compounds $[\text{Zr}(\text{tsb})]_n$ Polymer, $\text{H}_4(3\text{-methoxy})_4\text{tsb}$, and $\text{H}_4(\text{t-methoxy})_4\text{tsb}$, cm^{-1} ^a

Assignment	$[\text{Zr}(\text{tsb}) \cdot 1.7 \text{ DMSO}]_n$	$\text{H}_4(\text{tsb})$	$\text{H}_4[(3\text{-methoxy})_4\text{tsb}]$	$\text{H}_4[(5\text{-methoxy})_4\text{tsb}]$
(O-H) ν terminal ^c	3650 sh ^c			
(O-H) ν H-bonded or bridging	3430 br ^c	3500 w, br	3450 br	3450 br
(C=N) ν	1602 s ^c	1610 s	1612 } s 1605 }	1622 m 1337 m ^d
M-(O- ϕ) ν	1310 m ^c			
H(O- ϕ) ν		1275 ms	1268 sh	1270 s
$\text{H}_3\text{C}(\text{O-}\phi) \nu$ ^b			1250 s	1252 m
$\text{H}_3(\text{C-O}) \nu$ ^b			1228 w, sh	1228 w
DMSO (S-O) ν	1025 br			

^aKBr pellets; ^btentative assignments; ^cabbreviations: ν = stretching mode, sh = shoulder, br = broad, s = strong, m = medium, w = weak; ^dunknown assignment.

TABLE I. GPC and Viscosity Data for Polymeric Zr(tsb) in NMP.

Volume ^a	\bar{M}_n (PS) ^b	$[\eta]$ ^c	\bar{M}_η ^d
5.65	49,000	0.177±0.015	104,000±9,000
5.89	38,000	0.140±0.009	87,000±7,000
6.17	28,000	0.117±0.018	64,000±10,000
6.24	26,000	0.091±0.008	72,000±7,000
9.54	760 ^e	0.02 ±0.01	1,000± 500

^aRetention volume in mL on a 10^3 Angstrom Ultrastyrigel GPC column with NMP as the solvent. ^bPolystyrene equivalent number average molecular weight based on calibration with eleven standards. ^cIntrinsic viscosity in NMP at 30.0°C in dL/g. ^dMolecular weight based on viscosity/GPC universal calibration curve method. ^eModel monomeric zirconium Schiff-base chelate with a molecular weight of 690.

32. Carraher, C.E., Jr.; Sheats, J.E.; Pittman, C.U., Jr. "Organometallic Polymers." Academic Press, New York, 1978, pp. 1, 13, 25, 39, 53, 67, 87, 107, and 181.
33. Illingsworth, M.L.; Archer, R.D. Polyhedron, 1982, 1, 487.

16. Hill, W.E.; Atabay, N.; McAuliffe, C.A.; McCullough, F.P.; Razzoki, S.M. Inorg. Chim. Acta, 1979, 35, 35.
17. Archer, R.D.; Illingsworth, M.L. Inorg. Nucl. Chem. Lett., 1977, 13, 661.
18. Merrell, P.H.; Osgood, R.A. Inorg. Chim. Acta, 1975, 14, L33.
19. Archer, R.D.; Batschelet, W.H.; Illingsworth, M.L. J. Macromol. Sci. - Chem., 1981, A16, 261 gives a preliminary report on the polymer-based on a paper presented at an Am. Chem. Soc. Symposium; in part from Illingsworth, M. L., Ph. D. Dissertation, Univ. of Massachusetts, 1980.
20. Dudgeon, C.D., Ph.D. Dissertation, University of Massachusetts, Amherst, 1976.
21. Analyses by University of Massachusetts Microanalytical Laboratory.
22. Merrell, P.H.; Maheu, L.J. Inorg. Chim. Acta, 1978, 28, 47.
23. Kraemer, E.O. Ind. Eng. Chem., 1938, 30, 1200.
24. Carraher, C.E., Jr; Sheats, J.E.; Pittman, C.U., Jr. "Organometallic Polymers", Academic Press, New York, 1978, p. 90.
25. Reynolds, W.L. Progr. Inorg. Chem., 1970, 12, 1.
26. Conciatori, A.B.; Chenevey, E.C.; Bohrer, T.C.; Prince, A.E., Jr. J. Polym. Sci., C, 1967, 5, 49.
27. Syromiatnikov, W.; Prot, T. Polimery, (Warsaw), 1977, 22, 365; Chem. abstr., 1978, 89, 75485h.
28. Fuchs, O.; Suhr, H.H. "Polymer Handbook," 2nd Ed., Wiley, New York, 1975, p. iv-241.
29. Pittman, C.U. Jr.; Hirao, A. J. Polym. Sci. - Polym. Chem. Ed., 1977, 15, 1677. A viscosity of 0.140 corresponded to a M_n of 40,600.
30. Rodriguez, F. "Principles of Polymer Systems", McGraw-Hill, New York, 1970, p. 154.
31. Gillman, H.D.; Nannelli, P. Inorg. Chem. Acta, 1977, 23, 259.

REFERENCES AND FOOTNOTES

1. Karampurwala, A.M.; Patel, R.P.; Shah, J.R. Angew. Makromol. Chem., 1980, 89, 57; ibid., 87, 87.
2. Karampurwala, A.M.; Patel, R.P.; Shah, J.R. J. Macromol. Sci.-Chem., 1981, A15, 431 and 439.
3. Patil, M.S.; Shah, N.R.; Rama, A.K.; Karampurwala, A.M.; Shah, J.R. J. Macromol. Sci.-Chem., 1981, A16, 737.
4. Deshpande, U.G.; Shah, J.R. J. Macromol. Sci.-Chem., 1983, A20, 355.
5. Trent'ev, A.R.; Rode, V.V.; Nekrasov, L.I.; Rukhadze, E.G. Vysokomol. Soedin., 1960, 2, 1557; ibid., 1962, 4, 13.
6. Marvel, C.S.; Tarkoy, N.T. J. Am. Chem. Soc., 1957, 79, 6000; ibid., 1958, 80, 832.
7. Goodwin, H.A.; Bailar, J.C., Jr. J. Am. Chem. Soc., 1961, 83, 2467.
8. Manecke, G.; Wille, W.E. Makromol. Chem., 1970, 133, 61.
9. Sawodny, W.; Gruenes, R.; Reitzle, H. Angew. Chem., 1982, 94, 803; Angew. Chem. Suppl., 1982, 1662; and references cited therein.
10. Bottino, F.A.; Finocchiaro, P.; Libertini, E.; Mamo, A.; Recca, A. Polymer Commun., 1983, 24, 63.
11. Archer, R.D.; Day, R.O.; Illingsworth, M.L. Inorg. Chem., 1979, 18, 2908.
12. Sheats, J.E. Kirk-Othmer Ency. Chem. Tech., 3rd. ed., 1981, 15, 184.
13. Fay, R.C.; Howie, J.K. J. Am. Chem. Soc., 1979, 101, 115, and references cited therein.
14. Carraher, C.E., Jr. J. Macromol. Sci.-Chem., 1982, A17, 1293; and references cited therein.
15. Cummins, D.; McKenzie, E.D.; Milburn, H. J. Chem. Soc., Dalton Trans., 1976, 130.

either alone or as composites. Our aim is to obtain species with improved solubility, flexibility, high thermal stability, and extended conjugation.

ACKNOWLEDGMENT

We wish to thank Dr. P. C. Uden and Mr. E. E. Fox for the pyrolysis-gas chromatography analysis. We are also grateful to the U. S. Office of Naval Research, the U. S. Army Research Office and the University of Massachusetts Materials Research Laboratory for support of this work and to the referees of this journal for their constructive criticism of the original manuscript.

polymers have shown thermal stabilities in excess at 300°. ¹⁴

The close similarities between the polymer spectra and thermal data with those of the model system suggest that the chelation in the Zr(tsb) units is analogous to that observed by x-ray diffraction for Zr(dsp)₂. ¹¹ Thus, if the chelating part of the tsb⁴⁻ ligand is as flexible as the corresponding dsp²⁻ ligand, ^{11,15,16} then some degree of nonrigidity is possible in the polymer.

Condensation polymerizations using the water scavenger, 2,2'-dimethoxypropane, DMP, ³¹ were attempted, but no perceivable increases in the average polymer chain length were obtained. Thus, we conclude that either DMP does not diminish the rate of chain termination, or that imprecise stoichiometry limited the chain growth.

Coordination polymerization of pre-made ligands with reactive zirconium starting materials was also investigated. Stoichiometric (1:2) model reactions between either zirconium tetra-alkoxides or tetrakis-(acetylacetonato)zirconium(IV) and a quadridentate Schiff-base ligand did not produce clean products in high enough yields to warrant any further attempts at analogous polymerization reactions, although this method has met with some success in the past. ¹² Solubility problems limit polymer growth in this system by this method.

In light of the tetrakis(salicylaldehydato)zirconium(IV) chelate hydrolysis and the bis(quadridentate) ligand insolubility, ligand-centered polymerization ³² reactions of preformed eight-coordinate chelates have been considered. The hydrolytic stability of Zr(dsp)₂ which can be recrystallized from ordinary reagent-grade benzene and petroleum ether without decomposition, is encouraging in this regard. We have initiated studies in this area ³³ as we attempt to make long fibers of coordination polymers having unique properties, either alone or as composites. Our aim is to obtain species with improved

recrystallized $Zr(dsp)_2$ necessarily means that samples of the model compound undergo a very slow change upon standing in air at room temperature, but since acquisition of an O-H stretching mode at $3350-3600\text{ cm}^{-1}$ is the only change noted in the infrared absorbance spectrum, physical absorption of atmospheric water must be the only process occurring. Only upon heating to 240° does a chemical reaction apparently take place between the absorbed water and the Schiff-base complex. New peaks in the infrared at 1627 , 1163 , and 763 cm^{-1} after heating are consistent with this interpretation. Tentative assignments as a C=O stretch, a 1,2-disubstituted in-plane C-H bend, and a 1,2-disubstituted out-of-plane C-H bend, respectively, are consistent with a product resulting from hydrolysis of one imine bond.

Water produced during Schiff-base condensation presumably accounts for the analogous behavior of the polymer. The broad hydrogen bonded O-H stretch in the infrared spectrum of the polymer is consistent with water being present in addition to hydroxy end groups.²⁴ While the corresponding polymer weight loss also appears small in the TGA, extended heating in air at temperatures approximating this exothermic feature produces a much more substantial weight loss, up to 46% after one week; accordingly, this could be due to an on-going reaction with atmospheric moisture, or secondary reactions of hydrolyzed products. Several other Schiff-base polymers, Schiff-base coordination polymers and chelates show weight loss very near this temperature range.¹⁴

It should be pointed out that with quadridentate ligands other than Schiff-bases, zirconium coordination polymers might not show this feature. In the absence of this hydrolysis exotherm, the only other feature is a major decomposition due to combustion in air, TGA weight loss at 370° , with no decomposition occurring in nitrogen up to 500° . Other zirconium containing

The inherent viscosity values of up to about 0.18 dL/g for the polymer samples in NMP indicates a reasonable degree of polymerization, especially when coupled with the GPC results. The second order viscosity term in Kraemer's equation is unnecessary. A Universal Calibration treatment of the data provide an estimate of higher molecular weights as suggested above. The only reference point is the model monomer, which provides an indication that the retention volumes and viscosities are as anticipated. Attempts to estimate the molecular weight from the viscosity with the Mark-Houwink equation³⁰

$$[\eta] = KM^a \quad (3)$$

are difficult because no soluble coordination polymers similar to Zr(tsb) exist for which K and a values have been determined. Attempts to measure the absolute molecular weights directly have been fraught with insurmountable problems. The fluorescence of the polymer has precluded precise results through light scattering and attempts to use membrane osmometry have been thwarted by the instability of the membranes in NMP. Thus, we are stuck with the "ball park" figures of between 49,000 based on the direct GPC measurements relative to polystyrene and the 100,000 value from the Universal Calibration curve, again relative to polystyrene. We have chosen the more conservative number for our claims.

Since the endothermic loss of DMSO from the polymer represents desolvation, the 225-250° exotherm in the polymer DTA, and similarly for aged samples of Zr(dsp)₂, represents the first bond-breaking and bond-forming chemical reaction. The observation that this feature does not occur in freshly

separately dissolved in DMSO so that the dissolution rate would not be the rate determining step in the polymerization reaction. Formation of the deep-red color associated with the polymeric product begins almost instantaneously upon mixing of the solutions at room temperature.

The formation of light-diffracting films upon evaporation of the solvent is a property often shown by, but not limited to, soluble polymers. More concrete evidence is deduced from the GPC, viscosity and analysis results.

The GPC results of up to 49,000 (\bar{M}_n) indicate an average degree of polymerization (\bar{DP}) of up to about 80. The results could be underestimating the molecular weight, since the monomeric unit is 643 Daltons, and molecular weight models suggest each monomeric unit is about twice the size of a polystyrene unit. Thus an appreciably higher molecular weight is possible. On the other hand, the large orientation angle between ligands estimated from the x-ray study¹¹ might give a pseudo rigid-rod effect. Unfortunately no other heavy metal chelate polymers are available for comparison. Ferrocene polymers, the closest type, do appear to give results similar to organic polymers.²⁹

Consideration of the zirconium:ligand ratio of 1.018 and the elemental analysis corrected for the solvated DMSO suggests an average chain length of 20 to 50 units even if all of the end groups were hydroxides for the lowest molecular weight sample polymer in Table I. Given the equal probability of ligand end groups and of water to be coordinated along the chain or at the ends of the chains, the true degree of polymerization could be appreciably higher. The other samples have ligand to zirconium ratios of one to one within experimental error. Naturally, the effect of end groups on the elemental percentages becomes minimal, i.e. within analytical error, when large degrees of polymerization have been attained.

DISCUSSION



The dramatic difference in the solubility of the Zr(tsb) polymer relative to the free ligand¹⁸ or its derivatives²² or most other coordination polymers¹² is potentially very significant. Industrially, polymer solubility is very important; e.g., concentrated DMSO solutions called dopes are used for spinning certain polymer fibers.²⁶ Characterization is also more definitive for soluble species. One feature which may in part be responsible for this solubility difference is the puckered, perpendicularly arranged, quadridentate ligands anticipated from the model compound x-ray structure,¹¹ in which the ligands show no tendency to stack with either benzene solvate molecules or chelate ligands from adjacent molecules. Models of the polymer chains, assuming the described stereochemistry, also depict steric reasons for significantly reduced lattice forces (cf., the Figure). Nonrigid molecular motion may further hinder packing of the polymer chains. However, average chain length must also be considered as a major factor in comparing solubilities with other coordination polymers. Other ligand-forming polymerizations which allow extended chain lengths are rare.⁸

The Schiff-base polymerization reaction is known to be a high yield reaction both with and without transition metals.^{6-10,27} Also, the method used herein avoids the solubility problem associated with premade H₄tsb ligands. However, the production of water in the presence of hydrolytically reactive Zr(sal)₄¹⁷ is of particular concern. Thus, DMSO, which is known for its strong hydrogen-bonding with water²⁵ and its properties as a polymer solvent,^{26,28} was chosen as the reaction medium. Both reactants were


is the presence of a broad absorption at $3350-3600\text{ cm}^{-1}$ due to an O-H stretching mode. The heated sample, however, not only maintains an O-H stretching mode, but three new absorptions at 1627 , 1163 , and $763(\text{sh})\text{ cm}^{-1}$ indicate that a new organic species is present.

The final thermal gravimetric feature displayed by both zirconium species is a large weight loss due to burning in air. This process begins at a slightly lower temperature for the polymer (380°) than for the model compound (400°). This chemical change is corroborated by the DTA: In air, the huge corresponding exotherm actually begins at less than 300° for the polymer, and at about 400° for $\text{Zr}(\text{dsp})_2$. However, a rather dramatic difference occurs under nitrogen: whereas the anerobic decomposition of the model compound is almost coincident to its combustion temperature, the polymer shows no such decomposition at temperatures below 500° .

Pyrolysis-gas chromatographic results, by contrast, are of greatest value as a fingerprint method. As anticipated for compounds of similar chemical structure, the gas chromatograms are consistent with the production of several identical pyrolysis fragments in the polymer and the model monomer. Extended heating of polymer samples in air at temperatures approximating the small exotherm (240°C) produces considerably larger weight losses than those observed at this temperature during slow TGA scans. Approximately 22% and 46% weight losses were observed after 1 and 7 days, respectively, for the 1.7 DMSO solvate polymer. These weight losses are comparable to previous weight loss results for other metal-chelate Schiff-base polymers.^{6-10,14}

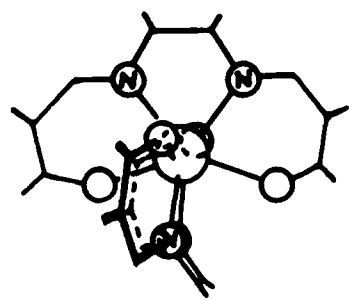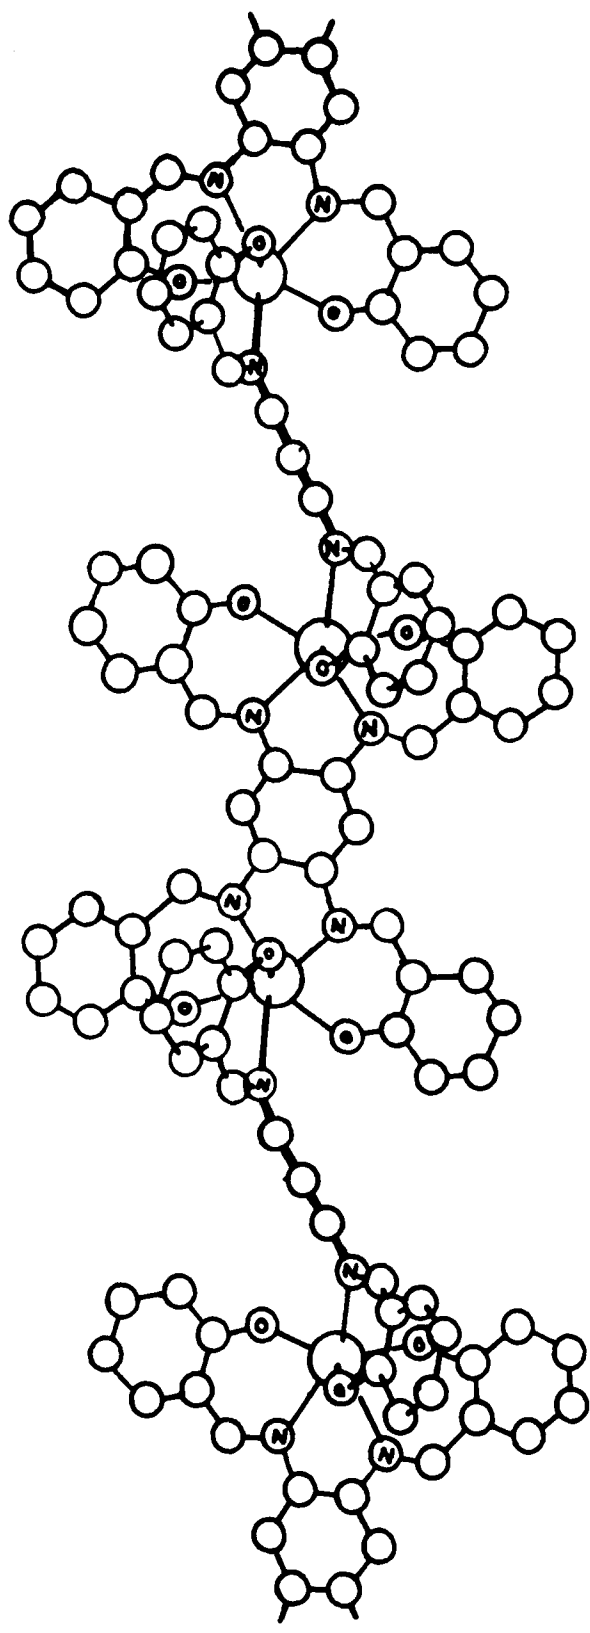

A

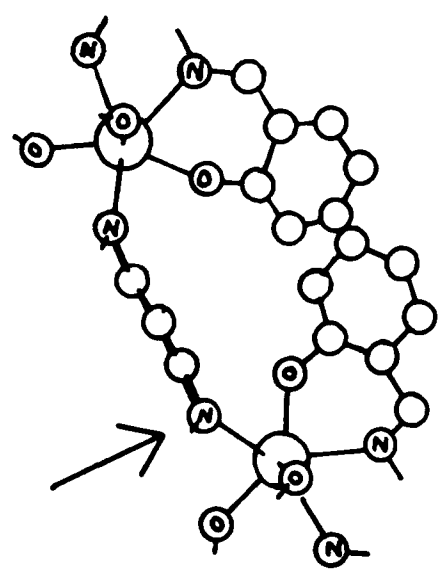

B

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 413 800 N. Quincy Street Arlington, Virginia 22217	2	Naval Ocean Systems Center Attn: Technical Library San Diego, California 92152	1
ONR Pasadena Detachment Attn: Dr. R. J. Marcus 1030 East Green Street Pasadena, California 91106	1	Naval Weapons Center Attn: Dr. A. B. Amster Chemistry Division China Lake, California 93555	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Washington, D.C. 20360	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1	Dean William Tolles Naval Postgraduate School Monterey, California 93940	1
Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Mr. Vincent Schaper DTNSRDC Code 2830 Annapolis, Maryland 21402	1
DTNSRDC Attn: Dr. G. Bosmajian Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1	Mr. A. M. Anzalone Administrative Librarian PLASTEC/ARRADCOM Bldg 3401 Dover, New Jersey 07801	1

TECHNICAL REPORT DISTRIBUTION LIST, 056

Dr. G. A. Somorjai
Department of Chemistry
University of California
Berkeley, California 94720

Dr. J. Murday
Naval Research Laboratory
Surface Chemistry Division (6170)
455 Overlook Avenue, S.W.
Washington, D.C. 20375

Dr. J. B. Hudson
Materials Division
Rensselaer Polytechnic Institute
Troy, New York 12181

Dr. Theodore E. Madey
Surface Chemistry Section
Department of Commerce
National Bureau of Standards
Washington, D.C. 20234

Dr. Chia-wei Woo
Department of Physics
Northwestern University
Evanston, Illinois 60201

Dr. Robert M. Hexter
Department of Chemistry
University of Minnesota
Minneapolis, Minnesota

Dr. J. E. Demuth
IBM Corporation
Thomas J. Watson Research Center
P.O. Box 218
Yorktown Heights, New York 10598

Dr. M. G. Lagally
Department of Metallurgical
and Mining Engineering
University of Wisconsin
Madison, Wisconsin 53706

Dr. Adolph B. Amster
Chemistry Division
Naval Weapons Center
China Lake, California 93555

Dr. W. Kohn
Department of Physics
University of California, San Diego
La Jolla, California 92037

Dr. R. L. Park
Director, Center of Materials
Research
University of Maryland
College Park, Maryland 20742

Dr. W. T. Peria
Electrical Engineering Department
University of Minnesota
Minneapolis, Minnesota 55455

Dr. Keith H. Johnson
Department of Metallurgy and
Materials Science
Massachusetts Institute of Technology
Cambridge, Massachusetts 02139

Dr. J. M. White
Department of Chemistry
University of Texas
Austin, Texas 78712

Dr. R. P. Van Duyne
Chemistry Department
Northwestern University
Evanston, Illinois 60201

Dr. S. Sibener
Department of Chemistry
James Franck Institute
5640 Ellis Avenue
Chicago, Illinois 60637

Dr. Arold Green
Quantum Surface Dynamics Branch
Code 3817
Naval Weapons Center
China Lake, California 93555

Dr. S. L. Bernasek
Princeton University
Department of Chemistry
Princeton, New Jersey 08544

TECHNICAL REPORT DISTRIBUTION LIST, 056

Dr. F. Carter
Code 6132
Naval Research Laboratory
Washington, D.C. 20375

Dr. Richard Colton
Code 6112
Naval Research Laboratory
Washington, D.C. 20375

Dr. Dan Pierce
National Bureau of Standards
Optical Physics Division
Washington, D.C. 20234

Professor R. Stanley Williams
Department of Chemistry
University of California
Los Angeles, California 90024

Dr. R. P. Messmer
Materials Characterization Lab.
General Electric Company
Schenectady, New York 22217

Dr. Robert Gomer
Department of Chemistry
James Franck Institute
5640 Ellis Avenue
Chicago, Illinois 60637

Dr. Ronald Lee
R301
Naval Surface Weapons Center
White Oak
Silver Spring, Maryland 20910

Dr. Paul Schoen
Code 5570
Naval Research Laboratory
Washington, D.C. 20375

Dr. John T. Yates
Department of Chemistry
University of Pittsburgh
Pittsburgh, Pennsylvania 15260

Dr. Richard Greene
Code 5230
Naval Research Laboratory
Washington, D.C. 20375

Dr. L. Kesmodel
Department of Physics
Indiana University
Bloomington, Indiana 47403

Dr. K. C. Janda
California Institute of Technology
Division of Chemistry and Chemical
Engineering
Pasadena, California 91125

Professor E. A. Irene
Department of Chemistry
University of North Carolina
Chapel Hill, North Carolina 27514

Dr. Adam Heller
Bell Laboratories
Murray Hill, New Jersey 07974

Dr. Martin Fleischmann
Department of Chemistry
Southampton University
Southampton SO9 5NH
Hampshire, England

Dr. John W. Wilkins
Cornell University
Laboratory of Atomic and
Solid State Physics
Ithaca, New York 14853

Dr. Richard Smardzewski
Code 6130
Naval Research Laboratory
Washington, D.C. 20375

Dr. H. Tachikawa
Chemistry Department
Jackson State University
Jackson, Mississippi 39217

TECHNICAL REPORT DISTRIBUTION LIST, 056

Dr. R. G. Wallis
Department of Physics
University of California
Irvine, California 92664

Dr. D. Ramaker
Chemistry Department
George Washington University
Washington, D.C. 20052

Dr. P. Hansma
Physics Department
University of California
Santa Barbara, California 93106

Dr. J. C. Hemminger
Chemistry Department
University of California
Irvine, California 92717

Professor T. F. George
Chemistry Department
University of Rochester
Rochester, New York 14627

Dr. G. Rubloff
IBM
Thomas J. Watson Research Center
P.O. Box 218
Yorktown Heights, New York 10598

Professor Horia Metiu
Chemistry Department
University of California
Santa Barbara, California 93106

Captain Lee Myers
AFOSR/NC
Bolling AFB
Washington, D.C. 20332

Professor Roald Hoffmann
Department of Chemistry
Cornell University
Ithaca, New York 14853

Dr. R. W. Plummer
Department of Physics
University of Pennsylvania
Philadelphia, Pennsylvania 19104

Dr. E. Yeager
Department of Chemistry
Case Western Reserve University
Cleveland, Ohio 41106

Professor D. Hercules
University Pittsburgh
Chemistry Department
Pittsburgh, Pennsylvania 15260

Professor N. Winograd
Department of Chemistry
Pennsylvania State University
University Park, Pennsylvania 16802

Dr. G. D. Stein
Mechanical Engineering Department
Northwestern University
Evanston, Illinois 60201

Professor A. Steckl
Department of Electrical and
Systems Engineering
Kensselaer Polytechnic Institute
Troy, New York 12181

Professor G. H. Morrison
Department of Chemistry
Cornell University
Ithaca, New York 14853

Dr. David Squire
Army Research Office
P.O. Box 12211
Research Triangle Park, NC 27709

Dr. R. D. Archer
Chemistry Department
University of Massachusetts
Amherst, Massachusetts 01003

DL/413/83/01
056/413-2

TECHNICAL REPORT DISTRIBUTION LIST, 056

Dr. J. E. Jensen
Hughes Research Laboratory
3011 Malibu Canyon Road
Malibu, California 90265

Dr. W. Knauer
Hughes Research Laboratory
3011 Malibu Canyon Road
Malibu, California 90265

Dr. J. H. Weaver
Department of Chemical Engineering
and Materials Science
University of Minnesota
Minneapolis, Minnesota 55455

Dr. C. B. Harris
Department of Chemistry
University of California
Berkeley, California 94720

END

FILMED

4-85

DTIC