

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS - 1963 - A

AD-A159 480

②

HEADQUARTERS
OGDEN AIR LOGISTICS CENTER
UNITED STATES AIR FORCE
HILL AIR FORCE BASE, UTAH 84056

QUALIFICATION OF A NEW MAPO
SOURCE AND ERL-510 CURING AGENT
FOR MINUTEMAN STAGE I UF-212I LINER

PROPELLANT ANALYSIS LABORATORY

MANPA REPORT

NR 500(84)

OCTOBER 1984

DTIC
ELECTE
SEP 18 1985
A

DTIC FILE COPY

APPROVED FOR PUBLIC RELEASE, DISTRIBUTION UNLIMITED

85 09 13 080


MANPA REPORT
NR 500(84)

QUALIFICATION OF A NEW MAPO
SOURCE AND ERL-510 CURING AGENT
FOR MINUTEMAN STAGE I UF-2121 LINER


Author


JOHN A. THOMPSON, Chemist
Component & Combustion Test Unit


Statistical Review By


EDWARD ERICKSON, Mathematician
Data Analysis Unit

Engineering Review By


JOHN K. SCAMBIA, Project Engineer
Service Engineering

Approved By


ANTHONY J. INVERSO, Chief
Propellant Analysis Laboratory

October 1984

Ind Products & Ldg Gear Division
Directorate of Maintenance
Ogden Air Logistics Center
United States Air Force
Hill Air Force Base, Utah 84056

10/18
ABSTRACT

Thiokol Chemical Corporation/Wasatch Division uses MAPO in the production of UF-2121 liner. Thiokol changed MAPO vendors and, therefore, qualification of the new source MAPO was required.

Thiokol prepared specimens from the new source and also specimens from the original source which are to be used as the control material in the 10 year surveillance testing program. The specimens were transferred to Ogden ALC for testing and reporting of the data obtained.

This report includes the Quality Assurance test results for the first through the ninth time testing of the control and special specimens at Ogden Air Logistics Center ALC.

Statistical analysis of the test data showed that the physical properties of the new source compared closely to the old source of UF-2121 liner specimens.

In all instances, the mean data for the control and special specimens are well above the minimum requirements found in TWR-7857 REV A, Thiokol specimen data. Therefore, the capability of the liner from the new source material is expected to perform satisfactorily.

Handwritten notes and a checkmark are present in the right margin. A rectangular stamp contains the handwritten letters "AL" and a checkmark.



TABLE OF CONTENTS

	<u>Page</u>
Abstract	11
Introduction	1
Table 1, Test Conditions and Methods	3
Statistical Analysis	4
Test Results	6
Conclusions and Recommendations	8
Table 2, Test Data Summary (1975)	9
Table 3, Test Data Summary (1976)	9
Table 4, Test Data Summary (1977)	9
Table 5, Test Data Summary (1978)	10
Table 6, Test Data Summary (1979)	10
Table 7, Test Data Summary (1980)	10
Table 8, Test Data Summary (1981)	11
Table 9, Test Data Summary (1983)	11
Table 10, Test Data Summary (1984)	11
Table 11, Analysis of Covariance Results	12
Figure 1, Control Disc (Steel/Liner/Steel)	13
Figure 2, Special Disc (Steel/Liner/Steel)	14
Figure 3, Control Cup (Steel/Liner/Steel)	15
Figure 4, Special Cup (Steel/Liner/Steel)	16
Figure 5, Control Peel (Steel/Liner/Steel)	17
Figure 6, Special Peel (Steel/Liner/Steel)	18
DD-1473	19
Distribution List	21

INTRODUCTION

A. PURPOSE:

Quality assurance testing of specimens prepared from the new source of MAPO to assure that liner material for First Stage Minuteman Motors will perform as predicted.

B. BACKGROUND:

*Tris [1-(2 methyl) aziridinyl] phosphine oxide (MAPO) is used as a curing agent in the Minuteman Stage One UF-2121 liner. MAPO was produced by Immont Chemical (Immont) and shipped to Arsynco Incorporated (Arsynco) for purification and marketing. Immont sold the production rights for MAPO to Arsynco and terminated the production of raw MAPO in 1972.

Since MAPO is a critical ingredient in UF-2121 liner formulation, the source change for the manufacture of MAPO was considered a serious change. Therefore, it was necessary for Thiokol to conduct qualification testing on liner material using MAPO manufactured by Arsynco before it could be considered acceptable for use in Minuteman Stage I UF-2121 liner.

ERLA-500 was the qualified epoxy curing agent used with MAPO in the UF2121 liner. Union Carbide terminated their process for ERLA-500. ERLA-510 used in similar liners (i.e. UF-2137) was substituted for ERLA-500 and qualified with MAPO from the new source.

The test conditions and test methods are shown in Table I.

*TWR-7857 Rev A Report, J. W. Rabern

Qualification testing was performed by Thiokol and reported in TWR-7857 Rev A. In addition, specimens were prepared by Thiokol From new vendor's material and from the old source material for a "follow on" test program. These specimens were then transferred to Ogden ALC for a continuing surveillance test program designed to cover a ten year span. This has been extended to 12 years as shown below in the 12 year contingency sample code. The material from the old source will be used as the control samples.

The 12 year sampling plan is shown below. Those specimens identified for the tenth year were tested at this test period. The types of specimens are Disc (steel/liner/steel), Cup (steel/liner/TP-H1011), and Peel (broad-cloth/liner/TP-H1011). For the disc specimen, the adhesion between the liner and steel is the critical factor. For the cup specimen, the adhesion between the propellant and the liner is critical. For the peel specimen, the propellant to liner peel strength when pulled at 180°F is critical.

TWELVE YEAR CONTINGENCY AGING SAMPLE CODING

Age (yr)	Storage Temp (°F)	Disc (Sample Nr)		Cup (Sample Nr)		Peel (Sample Nr)	
		Control*	Special**	Control*	Special**	Control*	Special**
1	75	1-6	181-186	61-66	241-246	121-126	301-306
2	75	7-12	187-192	67-72	247-252	127-132	307-312
3	75	13-18	193-198	73-78	253-258	133-138	313-318
4	75	19-24	199-204	79-84	259-264	139-144	319-324
5	75	25-30	205-210	85-90	265-270	145-150	325-330
6	75	31-36	211-216	91-96	271-276	151-156	331-336
7	75	37-42	217-222	97-102	277-282	157-162	337-342
9	75	43-48	223-228	103-108	283-288	163-168	343-348
10	75	49-54	229-234	109-114	289-294	169-174	349-354
12	75	55-60	235-240	115-120	295-300	175-300	355-360

* Liner mix A73-11846 - Control or old MAPO source material

** Liner mix A73-11810 - Experimental MAPO

TABLE I

Test Conditions and Methods

<u>Group</u>	<u>Test</u>	<u>Condition</u>	<u>Config- uration</u>	<u>G085 Spec Code</u>	<u>Spec Per Cond</u>	<u>Total Number of Spec</u>	<u>Test Method</u>
Bond in Tension Disc	Tensile Adhesion OI#127-3	CHS 0.5 in/ min, Chart 5.0 in/min, 500 lbs full scale load 77°F + 2°	Discs	TV	Control 6 Special 6	12	A
Bond in Tension Cup	Tensile Adhesion OI#127-3	CHS 0.5 in/ min, Chart 5.0 in/min, 200 lbs full scale load 77°F + 2°	Cup	TC	Control 6 Special 6	12	A
180° Peel Specimens	Tensile Peel OI#127-3	CHS 10 in/min 77°F + 2° Chart 5 in/ min 20 lbs full scale load	Peel	TE	Control 6 Special 6	12	B

TEST CONDITIONS

A. Testing of tensile adhesion specimens was performed using an Instron testing instrument. Properties measured were maximum stress to the nearest pound and failure mode.

Steel disc specimens require a stress of about 240 psi. The recommended initial full scale load is 500 pounds. This instrument setting should be changed to another setting if the first reading goes off scale on the high side. If 500 psi is exceeded, then change the reading to 1000 psi full scale.

Cup adhesion specimens are tested with a stress of 200 lbs per sq inch; the recommended full scale load is 500 lbs.

B. Testing of 180° peel samples was performed using an Instron testing instrument. The physical property of the material to be determined is the average peel strength to the nearest pound per inch.

NOTE: Thiokol's procedure for Testing and Laboratory Mixing of UF-2121 Liner. SLP 400, 28 April 71.

STATISTICAL ANALYSIS

UF-2121 liner material is being tested under a twelve year program to determine whether or not differences exist between liner materials manufactured from two separate sources of curing agent (MAPO). Test specimens were manufactured in two groups; control, using original source curing agent, and special, using new source curing agent. The test specimens for these two groups are three kinds: disc, cup, and peel. For each specimen type within each test group the sample test size is six. Laboratory testing for nine test periods or ten years has been accomplished. Test data for the years 1975 through 1984 are contained in Tables 2 through 10, and columns are summarized using means and standard deviations.

With nine test periods accomplished, regression plots (figures 1 thru 6) were made to determine whether slope and elevation differences existed between control and special test data by using the analysis of covariance. The regression model $Y = a + bX$, using individual data points, was used in the regression analyses. The variance about the least squares trend line is used to compute a tolerance interval such that at the 90% confidence level 90% of the sample distribution falls within this interval. This tolerance interval is extrapolated 24 months past the age point pertaining to the oldest specimens tested. The statistical significance of the slope of the trend line is evaluated for each regression plot. If significant, it is an indication that change over time is occurring.

In determining differences in data pertaining to the two MAPO sources, analysis of covariance was employed to compare control and special data from the regressions for each of the three types of test specimens. For analysis of covariance results, see table 11. Taken at the five percent significance

level, the only difference found was in the disc data in the variance of the data away from the regression line.

An in-house statistical investigation of the high - low, see - saw data pattern at every other month has been conducted. All test samples in this quality assurance program were prepared and labeled for testing at Thiokol, then transferred to Ogden ALC for testing. An error in labeling has been considered and tested.

The data was isolated and recombined with all the high months grouped together as coming from the same parent population, and all low months were also grouped together. New regression lines were put through each isolated data grouping. The isolated high new source regression trend lines were then compared against the high old source trend lines for combinability, or both isolated sets of data coming from the same parent population. All isolated regression trend lines were compared using the Analysis of Covariance testing.

The results showed that the residual variances about the isolated regression trend lines are considerably tighter. The trend line slopes are almost an overlay of each other. The trend line elevations however are out of the 95% confidence level. The isolated trend lines are not completely comparable, therefore a labeling error could not be varified.

TEST RESULTS

The 1984 test data and the means for the respective control and special data are shown in table 10. In addition, for a convenient comparison, the 1975 through 1983 test data are included in tables 2 through 9.

The statistical analysis results for the 1984 testing are shown in table 10 with the regressions shown in figures 1 through 6.

DISC:

A statistically significant difference is shown for variance of test data in the MAPO source (table 11).

The regression curves show a statistically significant gradual decrease for both the control and special sample data (figures 1 and 2).

For 1984, the mean of the control and special data is 15.22 and 15.35 kg/sq cm respectively.

The minimum specification requirement according to TWR-7857 Rev A, is 12.30 kg/sq cm minimum. As seen in table 10, MANPA's data is above this minimum.

The failure mode was 100% cohesive in the liner for both the control and special specimens.

CUP:

There is no significant difference in variance, slope or elevation when comparing control and special regression data (table 11).

The regression curves show a statistically significant gradual decrease in maximum stress as the specimens age (figures 3 and 4).

According to TWR-7857 Rev A Report, the minimum requirement is 4.92 kg/sq cm. The data means are 9.44 kg/sq cm for the control and 9.58 kg/sq cm for the special specimens.

For the control specimens, the failure mode was 100% in the propellant on all specimens. For the special specimens, three specimens broke 100% in the propellant and three specimens broke 95% in the propellant with 5% at the propellant to liner interface.

PEEL:

No significant difference is shown for the variance, slope or elevation when comparing control with special regression data (table 11).

The regression curves (figures 5 and 6) show a statistically significant increase in peel strength with respect to the age of the specimens.

Thiokol reported (TWR-7857 Rev A) 0.679 and 0.732 kg/L* cm respectively for the control and special mean data at age six months. This compares with 1984 data of 0.81 and 0.80 kg/1 cm respectively for control and special mean data (table 10).

The mode of failure was 100% liner to propellant bond.

* Kilogram per linear centimeter.

CONCLUSIONS

Based on this analysis, the only statistically significant difference between the control and special specimens is the variance for disc specimens.

The disc and cup regressions show a gradual statistically significant decrease with the peel specimen data showing a statistically significant increase.

The strength of the specimens is well above the required minimum for disc and cup, and above that reported in Thiokol's testing for peel.

From the analysis of the data, the new source of raw material performs as well as the old source; and therefore is expected to perform satisfactorily.

RECOMMENDATIONS

It is recommended that the testing plan be continued to assure long range capability of the liner produced from the new source of material.

TABLE 2. TEST DATA SUMMARY FOR JULY 1975

DISC		CUP		PEEL							
Control	Special	Control	Special	Control	Special						
Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/L-cm	Nr Kg/L-cm						
1	17.085	181	17.225	61	241	11.601	121	0.6786	301	0.6786	
2	17.507	182	17.858	62	11.812	242	11.601	122	0.6786	302	0.6965
3	17.225	183	17.015	63	11.741	243	11.531	123	0.7143	303	0.6965
4	17.929	184	16.944	64	12.163	244	11.671	124	0.7500	304	0.6965
5	17.366	185	17.436	65	12.234	245	11.390	125	0.7679	305	0.7143
6	17.296	186	19.054	66	11.882	246	11.390	126	0.7858	306	0.6965
\bar{Y}	17.401		17.589		11.966		11.531		0.7292		0.6965
S	0.2943		0.7899		0.2191		0.1176		0.0458		0.0113

TABLE 3. TEST DATA SUMMARY FOR MAY 1976

DISC		CUP		PEEL							
Control	Special	Control	Special	Control	Special						
Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/L-cm	Nr Kg/L-cm						
7	15.116	187	14.483	67	247	13.288	127	0.9643	307	1.0536	
8	16.311	188	14.905	68	13.710	248	13.710	128	0.9286	308	1.0358
9	15.397	189	14.483	69	13.640	249	13.640	129	0.9286	309	1.0179
10	15.960	190	14.765	70	13.007	250	13.077	130	1.0179	310	1.0358
11	15.819	191	15.468	71	13.148	251	13.359	131	1.1072	311	1.0536
12	14.554	192	14.765	72	13.499	252	13.499	132	1.0001	312	1.0358
\bar{Y}	15.526		14.812		13.401		13.429		0.9911		1.0388
S	0.6356		0.3633		0.3088		0.2354		0.0675		0.0134

TABLE 4. TEST DATA SUMMARY FOR APRIL 1977

DISC		CUP		PEEL							
Control	Special	Control	Special	Control	Special						
Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/cm ²	Nr Kg/L-cm	Nr Kg/L-cm						
13	17.155	193	17.436	73	9.281	253	9.140	133	0.7322	313	0.7858
14	16.522	194	16.874	74	9.281	254	9.070	134	0.7143	314	0.7858
15	16.874	195	16.944	75	8.999	255	8.999	135	0.6786	315	0.7858
16	17.015	196	17.366	76	9.281	256	9.140	136	0.7500	316	0.7143
17	16.874	197	17.015	77	9.492	257	8.367	137	0.7500	317	0.7500
18	16.874	198	17.015	78	9.281	258	8.789	138	0.6429	318	0.7143
\bar{Y}	16.886		17.108		9.269		8.918		0.7113		0.7560
S	0.2107		0.2337		0.1570		0.2994		0.0429		0.0352

NOTE: Kg/L-cm = Kilograms per linear centimeter. Average peel is given for each peel parameter.

TABLE 5. TEST DATA SUMMARY FOR JUNE 1978

DISC		CUP				PEEL					
Control		Special		Control		Special					
Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/L-cm				
19	14.906	199	14.554	79	10.898	259	10.406	139	0.9109	319	1.0180
20	14.624	200	14.695	80	10.968	260	10.476	140	0.9823	320	1.0359
21	14.695	201	14.343	81	10.617	261	10.616	141	0.9466	321	1.0180
22	14.906	202	14.343	82	10.125	262	10.125	142	1.0002	322	1.0359
23	14.343	203	14.624	83	10.406	263	10.687	143	1.0716	324	1.0537
24	15.187	204	14.414	84	10.476	264	10.125	144	0.9466	326	0.9287
\bar{Y}	14.777		14.496		10.582		10.406		0.9764		1.0150
S	0.2898		0.1503		0.3166		0.2391		0.0561		0.0444

TABLE 6. TEST DATA SUMMARY FOR JUNE 1979

DISC		CUP				PEEL					
Control		Special		Control		Special					
Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/L-cm				
25	17.015	205	17.436	85	9.632	265	9.562	145	0.8572	325	0.7679
26	16.874	206	16.874	86	9.703	266	9.140	146	0.8393	326	0.7679
27	16.874	207	16.593	87	9.773	267	9.562	147	0.8572	327	0.9643
28	16.944	208	16.522	88	9.632	268	9.281	148	0.8572	328	0.7143
29	16.804	209	16.382	89	9.632	269	9.421	149	0.7679	329	0.7143
30	16.171	210	17.366	90	9.492	270	9.421	150	0.8036	330	0.7500
\bar{Y}	16.780		16.862		9.644		9.398		0.8304		0.7798
S	0.3070		0.4477		0.0934		0.1644		0.0370		0.0936

TABLE 7. TEST DATA SUMMARY FOR SEPTEMBER 1980

DISC		CUP				PEEL					
Control		Special		Control		Special					
Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/L-cm				
31	15.116	211	14.764	91	9.281	271	11.109	151	0.9465	331	1.1965
32	14.905	212	14.413	92	10.054	272	10.265	152	1.0179	332	1.1786
33	14.624	213	14.202	93	10.616	273	10.898	153	1.0715	333	1.1072
34	14.905	214	14.272	94		274	10.687	154	1.1072	334	1.0536
35	15.678	215	13.870	95	9.894	275	9.491	155	1.0179	335	1.0358
36	15.116	216	14.272	96	10.054	276		156	1.0715	336	1.0358
\bar{Y}	15.057		14.284		9.998		10.490		1.0388		1.0846
S	0.3539		0.3188		0.4750		0.6397		0.0569		0.0613

TABLE 8. TEST DATA SUMMARY FOR JUNE 1984

DISC				CUP				PEEL			
Control		Special		Control		Special		Control		Special	
Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²
37	14.905	217	16.874	97	9.421	277	8.999	157		337	0.8036
38	15.819	218	16.944	98	9.210	278	9.070	158	0.7679	338	0.9018
39	15.116	219	15.187	99	9.281	279	9.351	159	0.7858	339	0.8126
40	15.749	220	16.101	100	9.351	280	8.437	160	0.8393	340	0.8304
41	15.890	221	15.679	101	9.632	281	9.562	161	0.8483	341	0.8572
42	15.468	222	15.608	102	9.351	282	9.843	162	0.8215	342	0.8929
\bar{Y}	15.491		16.066		9.374		9.210		0.8126		0.8929
S	0.4044		0.7151		0.1452		0.4911		0.0346		0.0413

TABLE 9. TEST DATA SUMMARY FOR SEPTEMBER 1983

DISC				CUP				PEEL			
Control		Special		Control		Special		Control		Special	
Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²
43	14.056	223	14.786	103	10.792	283	10.188	163	1.0358	343	1.2144
44	14.995	224	13.758	104	10.870	284	10.771	164	0.9822	344	1.1608
45	14.309	225	14.190	105	10.715	285	10.940	165	1.0179	345	1.2144
46	14.309	226	12.058	106	10.448	286	11.109	166	1.1251	346	1.2501
47	14.905	227	13.668	107	10.462	287	10.842	167	1.1786	347	1.1786
48	14.220	228	14.086	108	11.067	288	10.377	168	1.2144	348	1.0715
\bar{Y}	14.466		13.758		10.726		10.704		1.0923		1.1816
S	0.3874		0.9219		0.2402		0.3511		0.0941		0.0623

TABLE 10. TEST DATA SUMMARY FOR JUNE 1984

DISC				CUP				PEEL			
Control		Special		Control		Special		Control		Special	
Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²	Nr	Kg/cm ²
49	14.780	229	14.980	109	9.140	289	9.280	169	*	349	0.770
50	15.260	230	14.980	110	10.120	290	10.410	170	*	350	0.800
51	15.400	231	15.470	111	9.630	291	9.630	171	0.820	351	0.790
52	15.400	232	16.310	112	9.140	292	9.490	172	0.820	352	0.840
53	15.470	233	15.120	113	9.420	293	9.420	173	0.800	353	0.790
54	14.980	234	15.260	114	9.140	294	9.280	174	0.800	354	0.790
\bar{Y}	15.215		15.353		9.437		9.585		0.810		0.797
S	0.2757		0.5041		0.3921		0.4254		0.016		0.023


*Invalid sample

TABLE 11. ANALYSIS OF COVARIANCE RESULTS
 COMPARING CONTROL AND SPECIAL REGRESSION DATA

<u>Type of Data Compared</u>	<u>Parameter Compared</u>	<u>F-value</u>	<u>Degrees of Freedom</u>	<u>Covariance Results</u>
DISC	Variance	2.39	52,52	Significant
	Slope	0.01	1,104	Not Applicable
	Elevation	0.49	1,105	Not Applicable
CUP	Variance	1.25	51,49	Not Significant
	Slope	0.10	1,100	Not Significant
	Elevation	0.03	1,101	Not Significant
PEEL	Variance	1.50	52,49	Not Significant
	Slope	0.00	1,101	Not Significant
	Elevation	0.18	1,102	Not Significant

NOTE: The regressions are compared using the Analysis of Covariance at the 5% significance level. If comparison between residual variances is significant, further testing is not applicable.


F = 30.610115
 R = -0.608714
 S = 5.532540
 N = 54
 STORAGE COND = AMBIENT
 TEST COND = 77 DEG F AMB RH UF-2121 LINER
 $Y = (17.025588) + (-0.017572) \cdot X$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF P = SIGNIFICANT
 SIGNIFICANCE OF F = SIGNIFICANT
 DEGREES OF FREEDOM = 52
 $\sigma^2 = 1.041344$
 $S_D = 0.003176$
 $S_E = 0.634043$

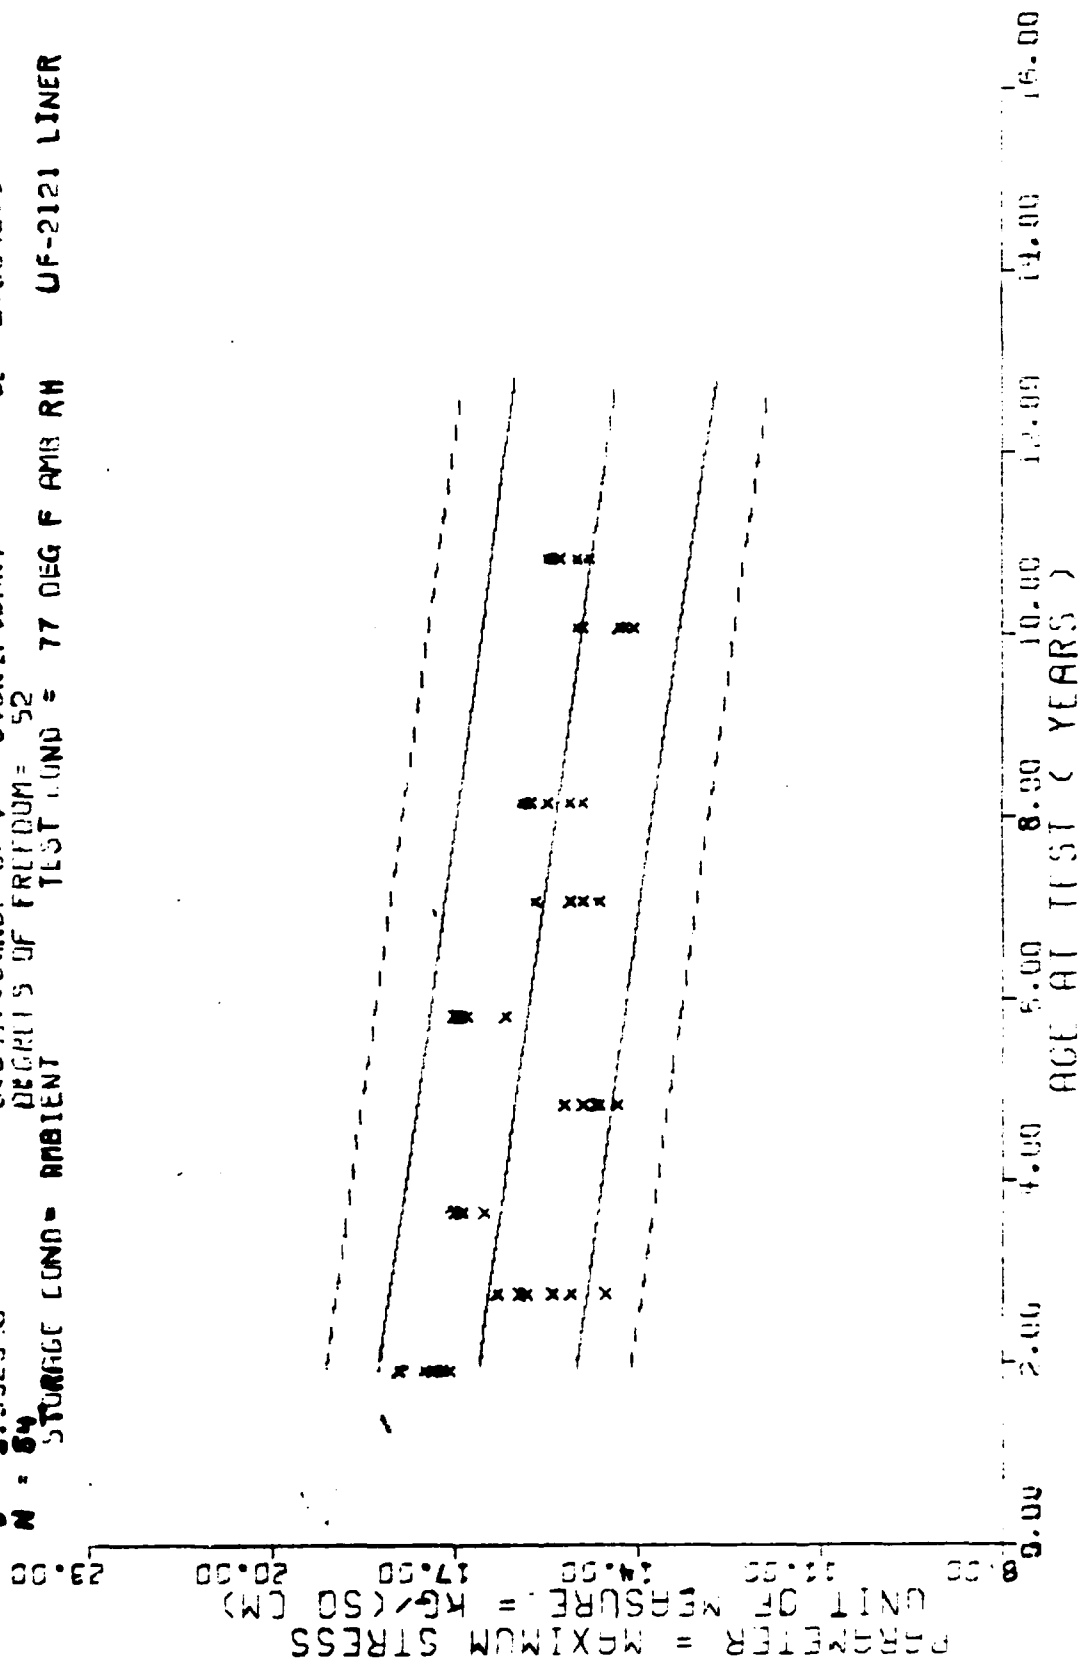

MAPD DISC./CONTROL (STEEL/LINER/STEE) TEST NR. 2


Figure 1

$y = (16.907752) + (-0.017870) * x$
 SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 52
 STORAGE COND = AMBIENT TEST COND = 77 DEG F AMB RH UF-2121 LINER
 F = 13.998222
 R = -0.460543
 t = 3.741420
 N = 54
 ST = 1.399749
 S_e = 0.004776
 SE = 1.254359

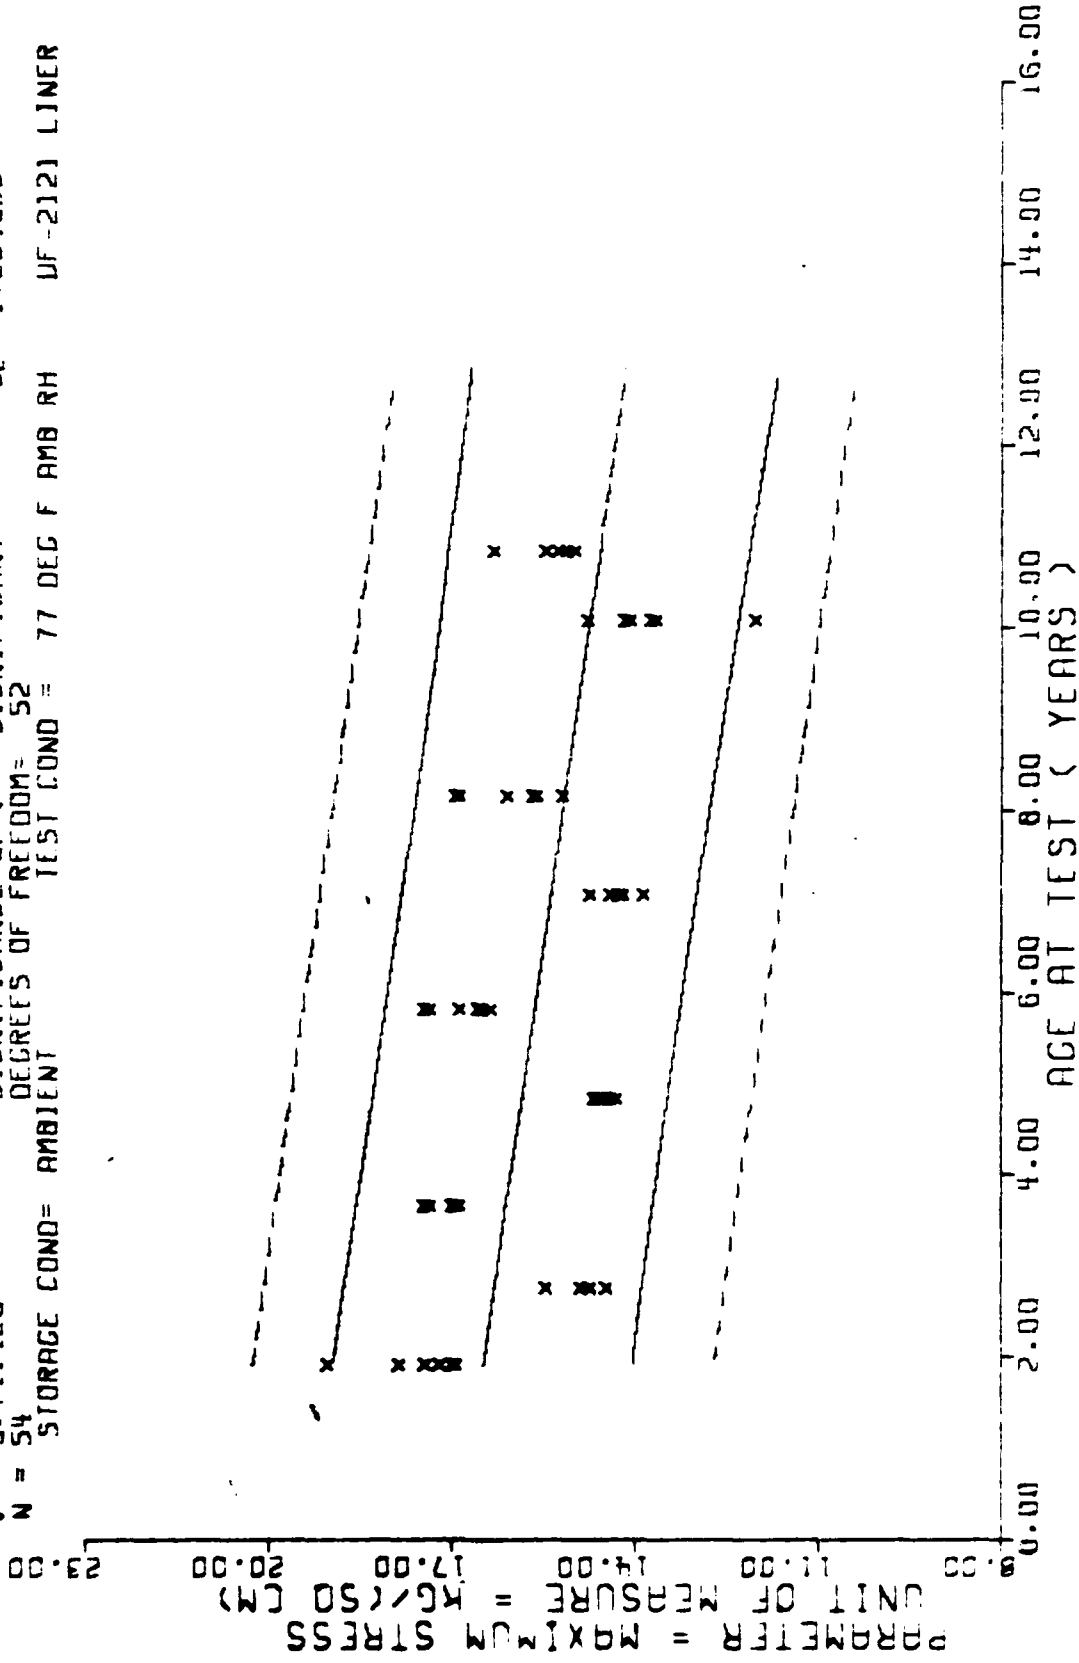

MAPD. SPECIAL DISC (STEEL/LINER/STEEL) TEST NR 9


$Y = (11.822525) + (-0.018803) * X$
 F = 17.886459 SIGNIFICANCE OF F = SIGNIFICANT $C_V = 1.306148$
 R = -0.517122 SIGNIFICANCE OF R = SIGNIFICANT $S_B = 0.004446$
 t = 4.229238 SIGNIFICANCE OF t = SIGNIFICANT $S_F = 1.129297$
 N = 51
 STORAGE COND= AMBIENT TEST COND = 77 DEG F AMB RH UF-2121 LINER

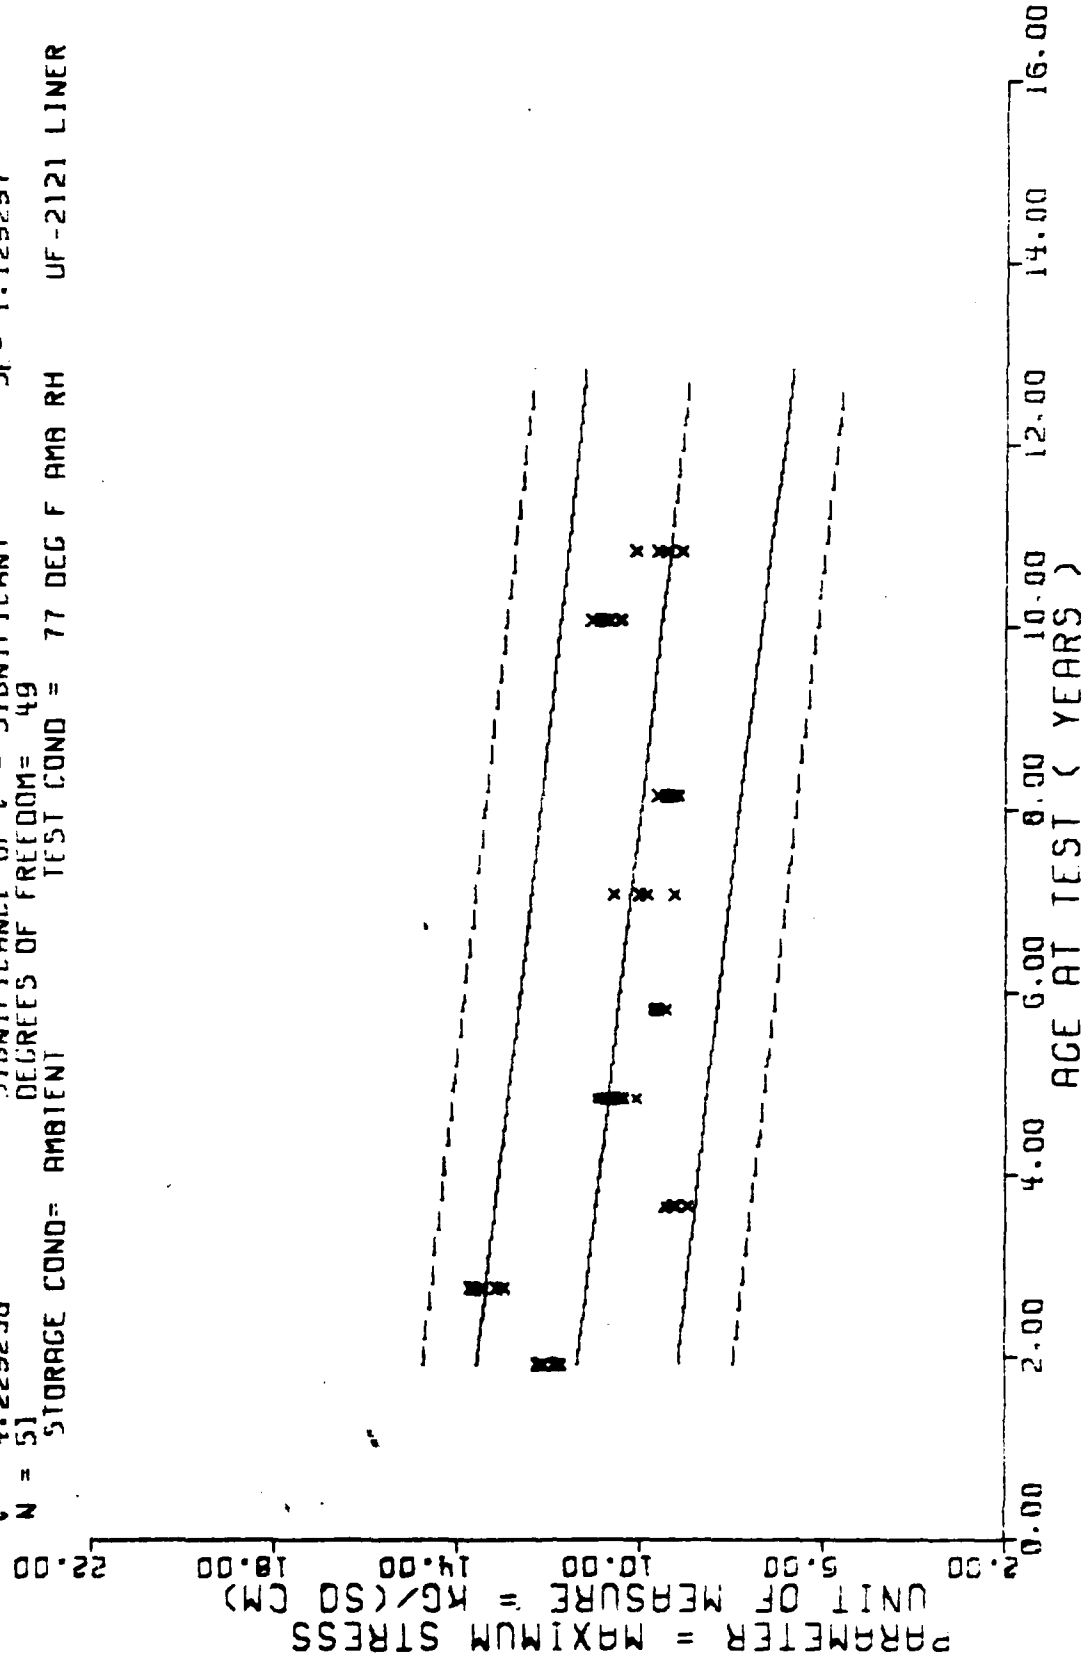

MAPO. CONTROL CUP (STEEL/LINER/STEEL) TEST NR 9

Figure 3

F = 12.152442) + (-0.016768) * X
 R = -0.438669 SIGNIFICANCE OF F = 0.016768
 t = 3.486036 SIGNIFICANCE OF R = SIGNIFICANT
 N = 53 SIGNIFICANCE OF t = SIGNIFICANT
 STORAGE COND= AMBIENT DEGREES OF FREEDOM= 51
 TEST COND = 77 DEG F AMB RH UF-2121 LINER

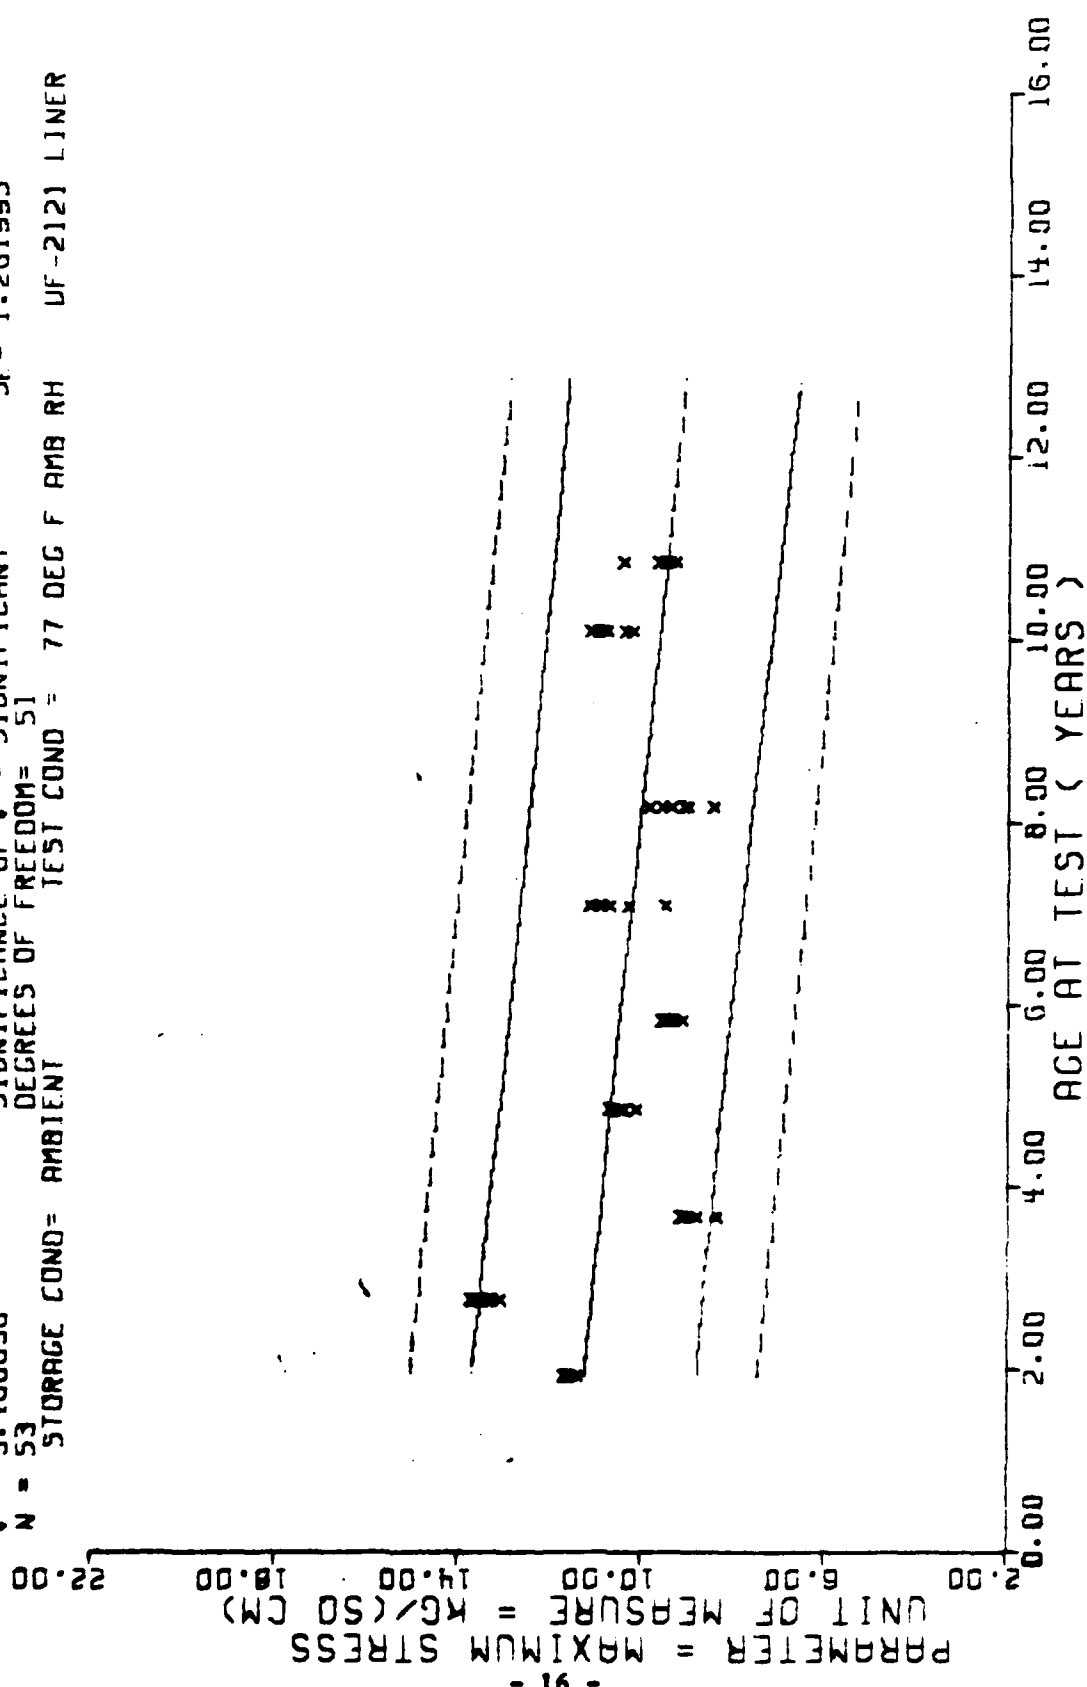

MAPO. SPECIAL CUP (STEEL/LINER/STEEL) TEST NR 9


Figure 4

$F = 7.052941$
 $R = 0.354710$
 $t = 2.655710$
 $N = 51$

$Y = (0.789379) + (0.001456) * X$

SIGNIFICANCE OF F = SIGNIFICANT
 SIGNIFICANCE OF R = SIGNIFICANT
 SIGNIFICANCE OF t = SIGNIFICANT
 DEGREES OF FREEDOM = 49

STORAGE COND = AMBIENT TEST COND = 77 DEG F AMB RH UF-2121 LINER

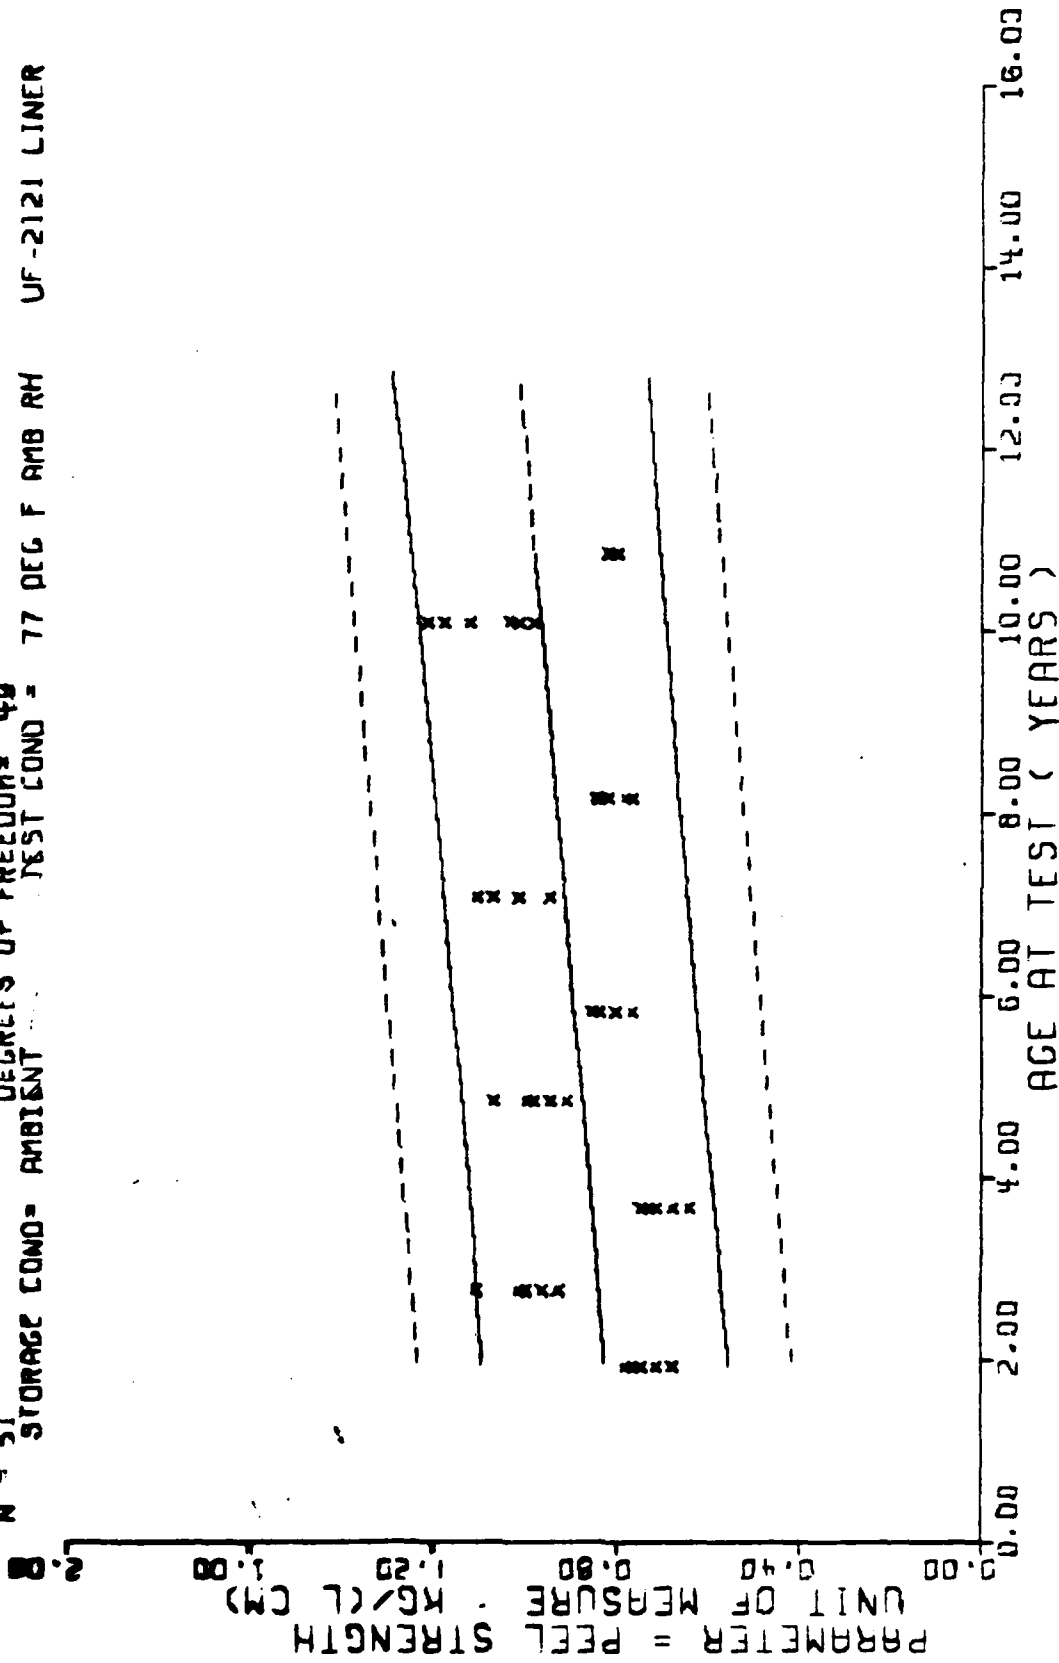


MAPO. CONTROL PEEL (STEEL/LINER/STEEL) TEST NR 0

Figure 5

$Y = (0.804859) + (0.001418) * X$
 SIGNIFICANCE OF F = 0.172681
 SIGNIFICANCE OF R = 0.000634
 SIGNIFICANCE OF t = 0.166514
 DEGREES OF FREEDOM = 52
 STORAGE COND = AMBIENT TEST COND = 77 DEG F AMB RH UF-2121 LINER

F = 4.998506
 R = 0.296134
 t = 2.235734
 N = 54

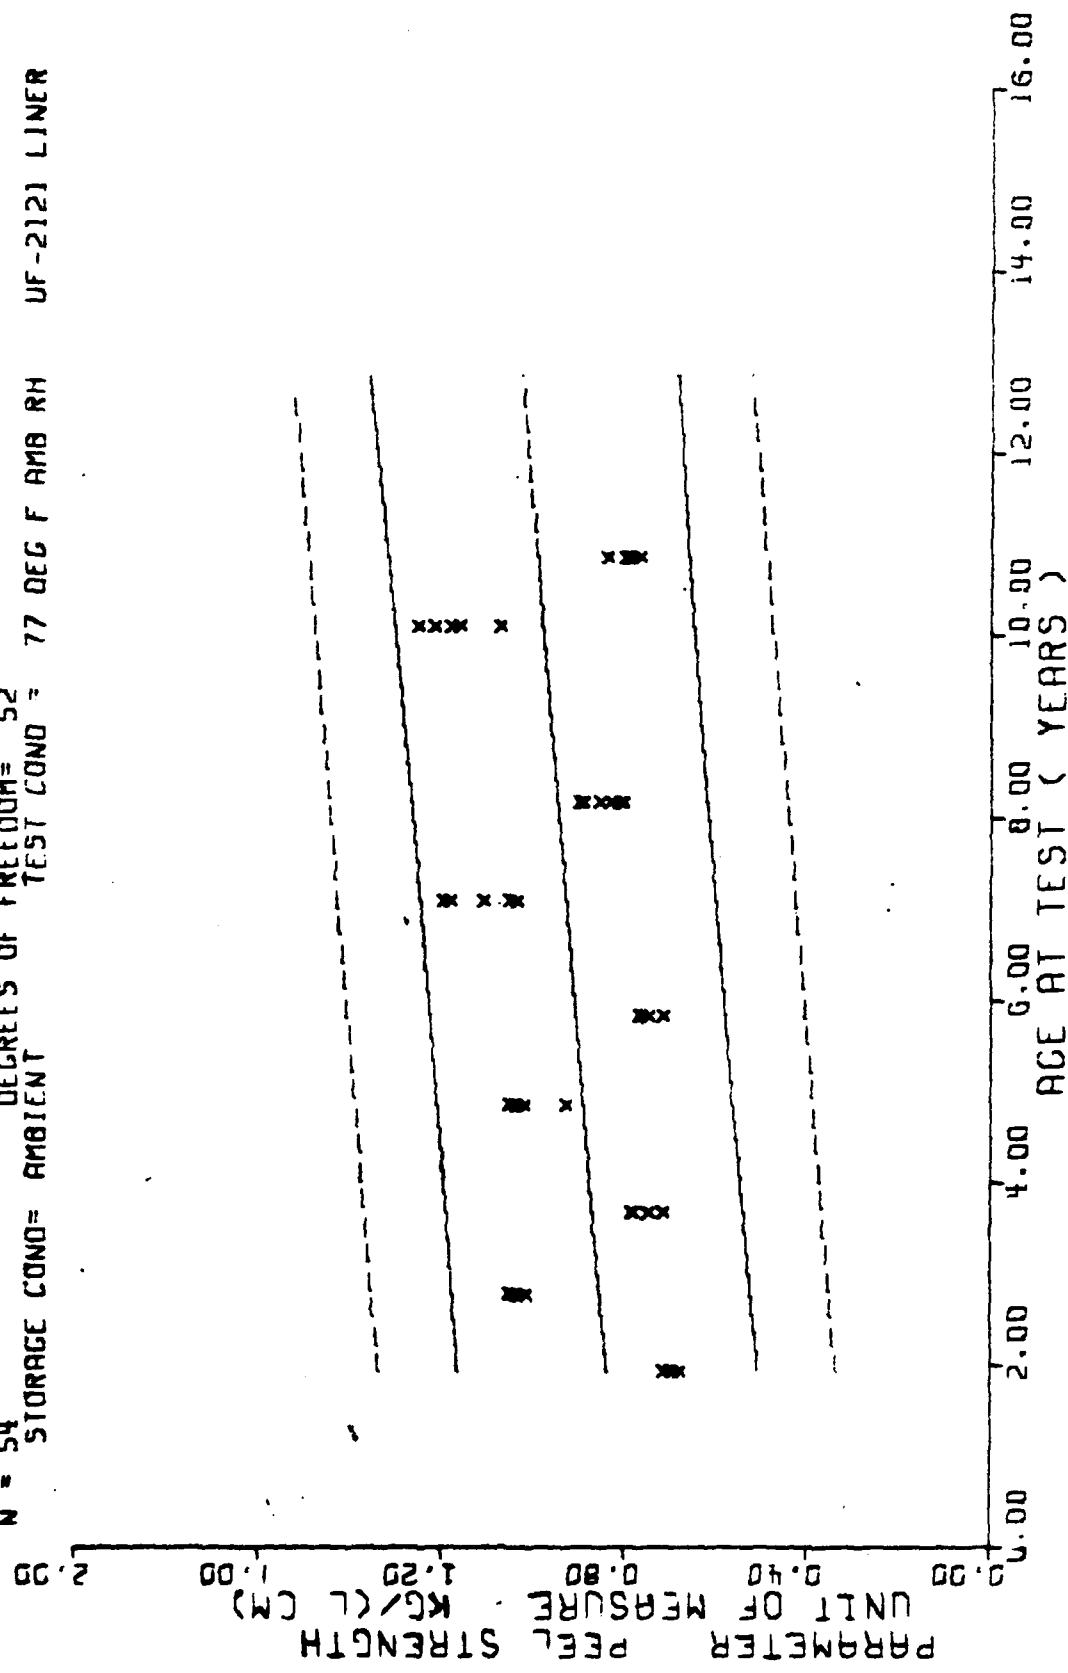

MAPQ. SPECIAL PEEL (STEEL/LINER/STEEL) TEST NR 9

Figure 6

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER MANPA REPORT NR 500(84) ✓	2. GOVT ACCESSION NO. AD-A159480	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Qualification of a new MAPO source and ERL-510 curing agent for Minuteman Stage I, UF-2121 liner		5. TYPE OF REPORT & PERIOD COVERED Test Results - Semi Annual
7. AUTHOR(s) JOHN A. THOMPSON		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Propellant Analysis Lab Directorate of Maintenance Hill AFB, UT 84056		8. CONTRACT OR GRANT NUMBER(s)
11. CONTROLLING OFFICE NAME AND ADDRESS Service Engineering Division Directorate of Materiel Management Hill AFB, UT 84056		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE October 1984
		13. NUMBER OF PAGES 27
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release, distribution unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Minuteman MAPO UF-2121 liner		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Thiokol Chemical Corporation/Wasatch Division uses MAPO in the production of UF-2121 liner. Thiokol changed MAPO vendors and, therefore, qualification of the new source MAPO was required. Thiokol prepared specimens from the new source and also specimens from the original source which are to be used as the control material in the 10 year surveillance testing program. The specimens were transferred to Ogden ALC for testing and reporting of the data obtained.		

This report includes the test results for the first through the ninth time testing of the control and special specimens at Ogden ALC.

Statistical analysis of the test data showed that the physical properties of the new source compared closely to the old source of UF-2121 liner specimens.

In all instances, the mean data for the control and special specimens are well above the minimum requirements found in TWR-7857 REV A, Thiokol specimen data. Therefore, the capability of the liner from the new source material is expected to perform satisfactorily.

DISTRIBUTION

	<u>NR</u> <u>COPIES</u>
OOALC	
MMWRBM	1
MMWRAM	1
DDC (TISIR) Cameron Station, Alexandria, VA 22314	2
SAMSO, Norton AFB, CA 92409	1
Attn: Mr. Sanford Collins, Bldg 562, Room 613	
AFPRO, Thiokol Chemical Corporation	2
Wasatch Division	
P.O. Box 524	
Brigham City, UT 84302	
(Cy to Larry Hales)	
AFRPL (MKPB) Edwards AFB, CA 93523	1
SAC (LGBM) Offutt AFB, NB 68113	1
U. S. Naval Ordnance Station, Indian Head, MD 20460	1
M. E. Loman, Code 3012A4	
Air Launched Weapons Branch	
Weapons Quality Engineering Center	
CPIA, Johns Hopkins University	1
Applied Physics Lab	
John Hopkins Road, Laurel, MD 20810	
Attn: Mr. Ronald D. Brown	

END

FILMED

11-85

DTIC