

AD-A103 410

DSC ELECTRICAL CONDUCTIVITY AND NMR STUDIES OF SALT
PRECIPITATION IN PPO C. (U) HUNTER COLL NEW YORK DEPT
OF PHYSICS AND ASTRONOMY J J FONTANELLA ET AL.

1/1


UNCLASSIFIED

01 JUL 87 TR-27 N00014-87-AF-00001

F/G 7/4

NL



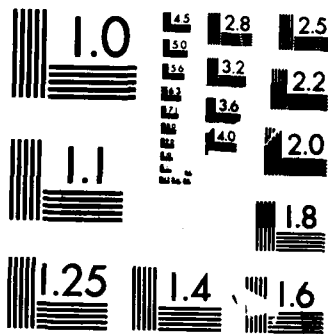

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD-A183 410

OFFICE OF NAVAL RESEARCH
Contract N00014-87-AF-00001
R&T Code 413d001-02
Technical Report No. 27

DSC, Electrical Conductivity, and NMR Studies of
Salt Precipitation in PPO Complexes

by

John J. Fontanella & Mary C. Wintersgill

Prepared for Publication

in the

British Polymer Journal

U. S. Naval Academy
Department of Physics
Annapolis, MD 21402-5026

July 1, 1987

DTIC
ELECTE
S D
JUL 27 1987
E

Reproduction in whole or in part is permitted for
any purpose of the United States Government

* This document has been approved for public release
and sale; its distribution is unlimited

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION / AVAILABILITY OF REPORT This document has been approved for public release and sale; its distribution is unlimited.	
2b. DECLASSIFICATION / DOWNGRADING SCHEDULE		5. MONITORING ORGANIZATION REPORT NUMBER(S)	
4. PERFORMING ORGANIZATION REPORT NUMBER(S) 27			
6a. NAME OF PERFORMING ORGANIZATION U. S. Naval Academy	6b. OFFICE SYMBOL (if applicable)	7a. NAME OF MONITORING ORGANIZATION	
6c. ADDRESS (City, State, and ZIP Code) Physics Department Annapolis, MD 21402-5026		7b. ADDRESS (City, State, and ZIP Code)	
8a. NAME OF FUNDING / SPONSORING ORGANIZATION Office of Naval Research	8b. OFFICE SYMBOL (if applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER	
8c. ADDRESS (City, State, and ZIP Code) 800 N. Quincy Street Arlington, VA 22217-5000		10. SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO. 61153N	PROJECT NO. RR013-06-0C
		TASK NO. 627-793	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) DSC, Electrical Conductivity, and NMR Studies of Salt Precipitation in PPO Complexes (Unclassified)			
12. PERSONAL AUTHOR(S) John J. Fontanella and Mary C. Wintersgill			
13a. TYPE OF REPORT Interim	13b. TIME COVERED FROM 86/10/1 TO 87/9/30	14. DATE OF REPORT (Year, Month, Day) 1987 July 1	15. PAGE COUNT 16
16. SUPPLEMENTARY NOTATION			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUBGROUP	
		Prepared for publication in the British Polymer Journal	
19. ABSTRACT (Continue on reverse if necessary and identify by block number)			
<p>DSC and electrical conductivity measurements of PPO complexed with NaI and KSCN are reported. In addition, 23 NMR measurements of PPO8NaI, both at ambient and elevated pressure (2.0 kbar) have been performed. The DSC data clearly indicate that the salt precipitates out of the complexes at about 85° for NaI and 60°C for KSCN. These effects are manifested by a dramatic departure of the conductivity from VTF behavior, and a relatively sharp drop in mobile Na concentration deduced from NMR measurements at somewhat elevated temperature (about 80°C). High pressure NMR linewidth measurements are consistent with a pressure-induced increase in the glass transition temperature.</p> <p><i>potassium thiocyanate</i></p> <p><i>solid solution</i> <i>Iodide</i></p>			
20. DISTRIBUTION / AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL John J. Fontanella		22b. TELEPHONE (Include Area Code) 301-267-3487	22c. OFFICE SYMBOL

DSC, Electrical Conductivity, and NMR Studies
of Salt Precipitation Effects in PPO Complexes

Mary C. Wintersgill and John J. Fontanella

Physics Department
U.S. Naval Academy
Annapolis, MD 21402 U.S.A

Steven G. Greenbaum and Krešimir J. Adamić

Physics Department
Hunter College of CUNY
New York, NY 10021 U.S.A.

Keywords: ion-conducting polymer; salt precipitation; NMR; DSC;
poly(propylene oxide)



Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

SYNOPSIS

DSC and electrical conductivity measurements of PPO complexed with NaI and KSCN are reported. In addition, ^{23}Na NMR measurements of PPO_8NaI , both at ambient and elevated pressure (2.0 kbar) have been performed. The DSC data clearly indicate that the salt precipitates out of the complexes at about 85°C for NaI and 60°C for KSCN. These effects are manifested by a dramatic departure of the conductivity from VTF behaviour, and a relatively sharp drop in mobile Na concentration deduced from NMR measurements at somewhat elevated temperature ($\sim 80^\circ\text{C}$). High pressure NMR linewidth measurements are consistent with a pressure-induced increase in glass transition temperature.

INTRODUCTION

Poly(propylene oxide) (PPO) is known to form amorphous ion conducting complexes with alkali metal salts.¹⁻³ Previous studies of PPO complexed with LiClO_4 ² and NaClO_4 ³ have shown that large scale segmental motion of the polymer chains is principally responsible for ionic transport, in general agreement with the results of a wide array of recent investigations. The studies in our laboratories^{2,3} can be summarized briefly as follows. The electrical conductivity temperature dependence is best described by a VTF-type relation⁴

$$\sigma = A T^{-1/2} \exp[-E_a/k(T - T_0)] \quad (1)$$

where E_a is the apparent activation energy and T_0 is the temperature of "zero configurational entropy", about 40-50 K below the glass transition temperature, T_g . The temperature dependence of the electrical relaxation time associated with the σ -relaxation which governs the glass to rubber transition in pure PPO can be described in an analogous manner. It has been shown that the activation energies for conductivity in the complexes and electrical relaxation in pure PPO are the same when one takes into account the different T_0 values associated with each material. Similarly, activation volumes for conductivity derived from variable pressure data in the complexes and the σ -relaxation in PPO were shown to be the same in a given temperature interval relative to T_0 .

²³Na NMR studies in $\text{PPO}_3\text{NaClO}_4$ have shown that: (1) generation of mobile ions is a weakly thermally activated process that accounts for only a minor contribution to the overall conductivity; (2) NMR signals associated with the mobile fraction of Na ions exhibit motional line-narrowing beginning in a small temperature interval above T_g . These results, taken together, demonstrate the importance of polymer chain mobility to ion transport, in general agreement with a wide array of recent investigations.

The present study concerns related work on PPO:NaI and PPO:KSCN complexes. In particular, it is observed that these materials

exhibit behaviour similar to that of previously investigated PPO complexes, however they become unstable at moderate temperatures ($<100^{\circ}\text{C}$). As will be discussed, the instability is manifested ultimately by the separation of the salt from the polymer.

We have performed differential scanning calorimetry (DSC), electrical conductivity and ^{23}Na nuclear magnetic resonance (NMR) measurements on PPO_8NaI . The NMR measurements were performed both at ambient pressure and at applied hydrostatic pressure up to 2 kbar (0.2 GPa). In addition, DSC and conductivity data for PPO_8KSCN are presented.

EXPERIMENTAL

The host material studied was Parel 58 (Hercules, Inc.) elastomer which is a sulfur-vulcanizable copolymer of propylene oxide and allyl glycidyl ether. As the primary constituent is propylene oxide, the material will be referred to throughout this paper as PPO. The samples were prepared by solution casting using anhydrous methanol as the solvent and commercially obtained NaI, which was heated at 100°C in a vacuum oven overnight, as the salt. All procedures including loading of the samples into the various sample holders were carried out in a dry box; the sample for the NMR measurements was sealed in a glass tube under dry nitrogen. For the high pressure measurements, the sample was loaded into the rf coil in a N_2 glove bag and then immersed in the pressure transmitting fluid (3M - Fluorinert) contained in the pressure cell. The details regarding the DSC, electrical conductivity and NMR equipment and techniques are given elsewhere.^{2,3}

RESULTS

The DSC results for PPO_8NaI are shown in Fig. 1. Results for uncomplexed PPO are included for comparison. It is clear that the complexed material is highly amorphous in that it exhibits a strong glass transition with a "central" T_g of about 6°C . (The "onset" T_g is about 0°C and the "end" is at about 12°C .) Consequently, T_g is about 68°C higher than for the uncomplexed material for which the

"central" glass transition temperature is about -62°C as shown in Fig. 1c. An increase in T_g with the addition of salt to PPO is a well known phenomenon².

In addition, in the DSC studies for PPO_8NaI , a strong, sharp endothermic event is observed at about 100°C . In order to obtain information concerning this feature, the material was annealed at 175°C , quenched to -140°C as rapidly as possible in situ, and the DSC studies repeated. Typical results for the quenched material after annealing at temperatures above 140°C are shown in Fig. 1b. In all cases, a strong glass transition typical of uncomplexed PPO is observed. In addition, there is a high temperature exothermic event followed by an endotherm. Similar behavior has been observed for $\text{PPO}_8\text{NaClO}_4$ where it was concluded that the high temperature endotherm is due to the salt coming out of the polymer.³ The primary evidence is that only the glass transition due to uncomplexed PPO is observed after quenching from temperatures above that of the sharp endotherm. Further, the material exhibits the original behavior (Fig. 1a) after allowing the sample to sit at room temperature overnight, i.e. the salt redissolves in the polymer. Salt precipitation has been observed spectroscopically for PPO containing NaSCN .⁵

In order to gain further evidence for this effect, electrical conductivity studies were performed. (It was not possible to perform such studies for $\text{PPO}_8\text{NaClO}_4$ as the salt precipitation temperature was outside the range of the conductivity apparatus.) The results are shown in Fig. 2. It is seen that the electrical conductivity begins to deviate from its lower temperature behavior at about 85°C . In order to demonstrate this more quantitatively, the data in the temperature range 280-355 K were analyzed with equation (1) with the adjustable parameters A , E_a , and T_0 . A non-linear least squares fit of eq. (1) to the data was carried out and the results are $E_a = 0.093$ eV, $T_0 = 199.3$ K, and $\log_{10}A [(\Omega\text{-cm})^{-1} \text{K}^{1/2}] = -1.1$. The RMS deviation in $\log_{10}\sigma$ was 0.008. These best-fit values are close to those observed for other salts in PPO. However, they are not as reliable due to the limited temperature range covered, and further, the high temperature cut-off (where salt precipitation becomes

important) is merely an estimate. In fact, the value for T_0 is about 80 K lower than the "central" T_g , which is a larger difference than expected.

A general feature of the ^{23}Na NMR results is the coexistence of two separate lineshape components with substantially different spin-lattice relaxation times (T_1) and linewidths. As in previous studies of similar complexes, the long- T_1 and broad component is attributed to bound Na species while the short- T_1 and narrow component arises from mobile Na^+ ions.³ The ratio of the narrow line to broad line intensities as a function of reciprocal temperature is plotted in Fig. 3. That the difference between the lowest temperature value and the maximum value (occurring just above room temperature) is only about a factor of ten is indicative of the relatively minor role that "carrier generation" plays in the overall conductivity, which changes by more than four orders of magnitude over the same temperature range. The salt precipitation is manifested as a sharp drop in mobile ion concentration above 80°C.

Figure 4 is a plot of ^{23}Na resonance linewidth (full width at half maximum) as a function of temperature. The open symbols denote partially saturated resonances which correspond to the mobile sodium population. The solid symbols refer to the total (unsaturated) linewidth. As in previous work³, the linewidths of the mobile and bound Na's are nearly indistinguishable below T_g , only their T_1 values are distinct. It is clear from the data that motional narrowing occurs above T_g , again in agreement with previous studies. The increase in linewidth above ~ 60°C is attributable to rapid spin-lattice relaxation ($T_1 \sim 300 \mu\text{s}$) which introduces a lifetime broadening contributions to the linewidth.

The application of hydrostatic pressure (up to several kbar) has been shown to result in a decrease in conductivity of PPO complexes^{2,3}. In order to obtain a better understanding of the mechanisms involved, we have performed some preliminary high pressure NMR measurements. Figure 5 displays ^{23}Na absorption spectra (both lineshape components are present in each spectrum) at ~ 40°C, where motional narrowing effects are apparent. The bottom

spectrum corresponds to ambient pressure, while the top spectrum was acquired at 2.0 kbar (0.2 GPa). The effect of the applied pressure is to broaden the resonance by about 25% to approximately the linewidth of the sample at lower temperatures (below T_g). This result is consistent with increases in T_g with pressure deduced from conductivity measurements^{2,3}. It is not presently known whether these phenomena simply reflect the pressure dependence of T_g , or are indicative of more subtle ion-polymer interactions. High pressure DSC measurements are currently underway in order to determine directly the T_g pressure-dependence. Conductivity vs. pressure studies, which may shed light on the salt precipitation process, are also in progress.

Another example of this salt precipitation is evident upon viewing the data for PPO_0KSCN , shown in Figs. 6 and 7. For this material, the salt comes out of the polymer at a lower temperature, about 60°C as seen by a sharp endotherm at about 60°C in Fig. 6. That the material was complexed is shown by the single glass transition temperature at about -25°C. Once again, upon thermal treatment, the glass transition disappears with the appearance of an uncomplexed PPO glass transition. This material is interesting because the melting endotherms for the salt are at relatively low temperature as shown in Fig. 6a. As shown in Figs. 6b and 6c, similar endotherms are observed in the polymer after heating above 60°C. Since the salt precipitation occurs at a relatively low temperature, the effect on the electrical conductivity is quite dramatic as shown in Fig. 7.

CONCLUSIONS

PPO complexed with NaI has been shown to exhibit the same general ion-conducting properties as other PPO-salt complexes at lower temperatures, whereas salt precipitation effects are observed in the former above ~ 85°C. The salt precipitation is manifested by (i) a relatively sharp endothermic "event" in the DSC, and subsequent observation of a pure PPO glass transition (after quenching); (ii) departure of the electrical conductivity from VTF-type behavior at elevated temperatures; (iii) a sharp drop in mobile

Na concentration, deduced from NMR measurements, above $\sim 80^{\circ}\text{C}$. PPO complexed with KSCN exhibits even more dramatic salt precipitation effects, as evidenced by corresponding features in the DSC and conductivity data occurring at a lower temperature ($\sim 60^{\circ}\text{C}$) as well as observation of KSCN melting endotherms in the complex. Preliminary NMR measurements on PPO_8NaI at an applied hydrostatic pressure of 2.0 kbar (0.2 GPa) are consistent with a pressure-induced increase in T_g .

ACKNOWLEDGMENTS


The authors would like to thank Hercules, Inc. for supplying the Parel 58 elastomer. The assistance of Ms. Meng Chiao, Ms. Gillian Reynolds, and Mr. Yiu Sun Pak with the NMR measurements and data analysis is gratefully acknowledged. This work was supported in part by the Office of Naval Research and the PSC-CUNY Research Award Program.


REFERENCES

- 1) Armand M., Chabagno M., and Duclot M.J.; in: Fast Ion Transport in Solids, eds. Vashishta P., Mundy J.N., and Shenoy G.K. (North-Holland, Amsterdam, 1979), p. 131.
- 2) Fontanella J.J., Wintersgill M.C., Smith M.K., Semancik J., and Andeen C.G.; J. Appl. Phys., 1986, 60, 2665.
- 3) Greenbaum S.G., Pak Y.S., Wintersgill M.C., Fontanella J.J., Schultz J.W., and Andeen C.G.; J. Electrochem. Soc., in press.
- 4) Vogel, H., Physik Z., 1921, 22, 645; Tammann, V.G. and Hesse, Z., Anorg. Allg. Chem, 1926, 156, 245; Fulcher, G.S., J. Am. Ceram. Soc., 1925, 8, 339.
- 5) Teeters D. and Frech R.; Solid State Ionics, 1986, 18&19, 271.


FIGURE CAPTIONS


- Figure 1. DSC plot for a) uncomplexed PPO, b) as prepared PPO_8NaI , and c) PPO_8NaI after having been annealed at 175°C and quenched, in situ, to -140°C . Scanning rate is 10 K/min.
- Figure 2. Arrhenius plot of the electrical conductivity data for PPO_8NaI . The squares correspond to the data and the solid line is the best fit VTF equation (equation 1).
- Figure 3. Arrhenius plot of ^{23}Na narrow to broad line intensity ratios in PPO_8NaI .
- Figure 4. ^{23}Na linewidth in PPO_8NaI . The solid symbols denote the total linewidth while the open symbols refer to partially saturated resonances, reflecting the presence of only the mobile sodium population.
- Figure 5. ^{23}Na absorption spectrum in PPO_8NaI at 40°C . Bottom: ambient pressure; Top: applied hydrostatic pressure of 2 kbar (0.2 GPa).
- Figure 6. DSC plot for a) KSCN, b) PPO_8KSCN , c) PPO_8KSCN after having been annealed at 200°C and quenched, in situ, to -140°C , d) uncomplexed PPO. Scanning rate is 10 K/min.
- Figure 7. Arrhenius plot of the electrical conductivity data for PPO_8KSCN . The solid line connects the data points.

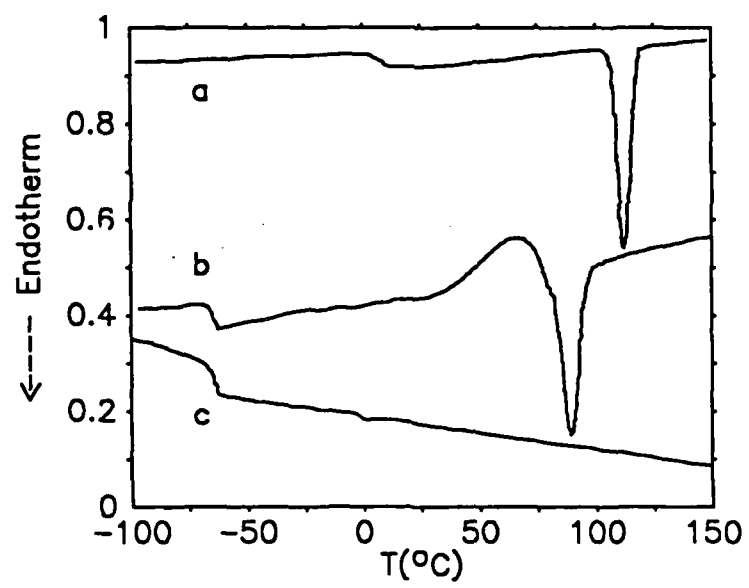


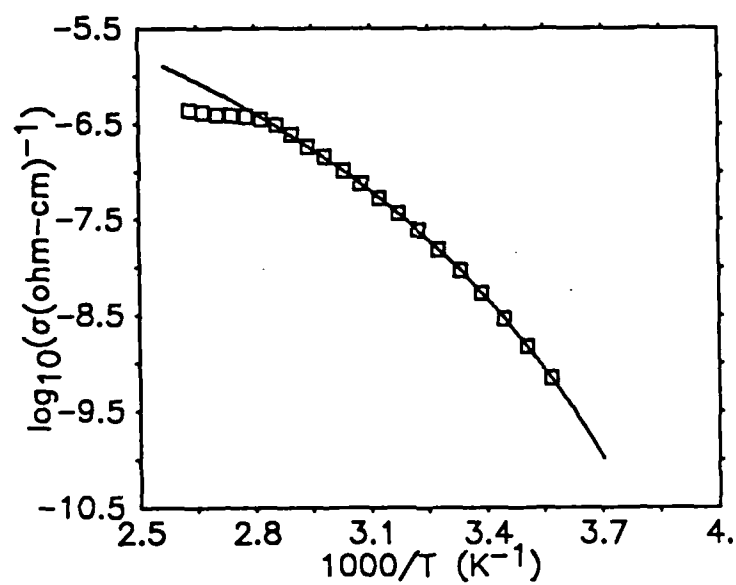


Relative intensity (N/B)

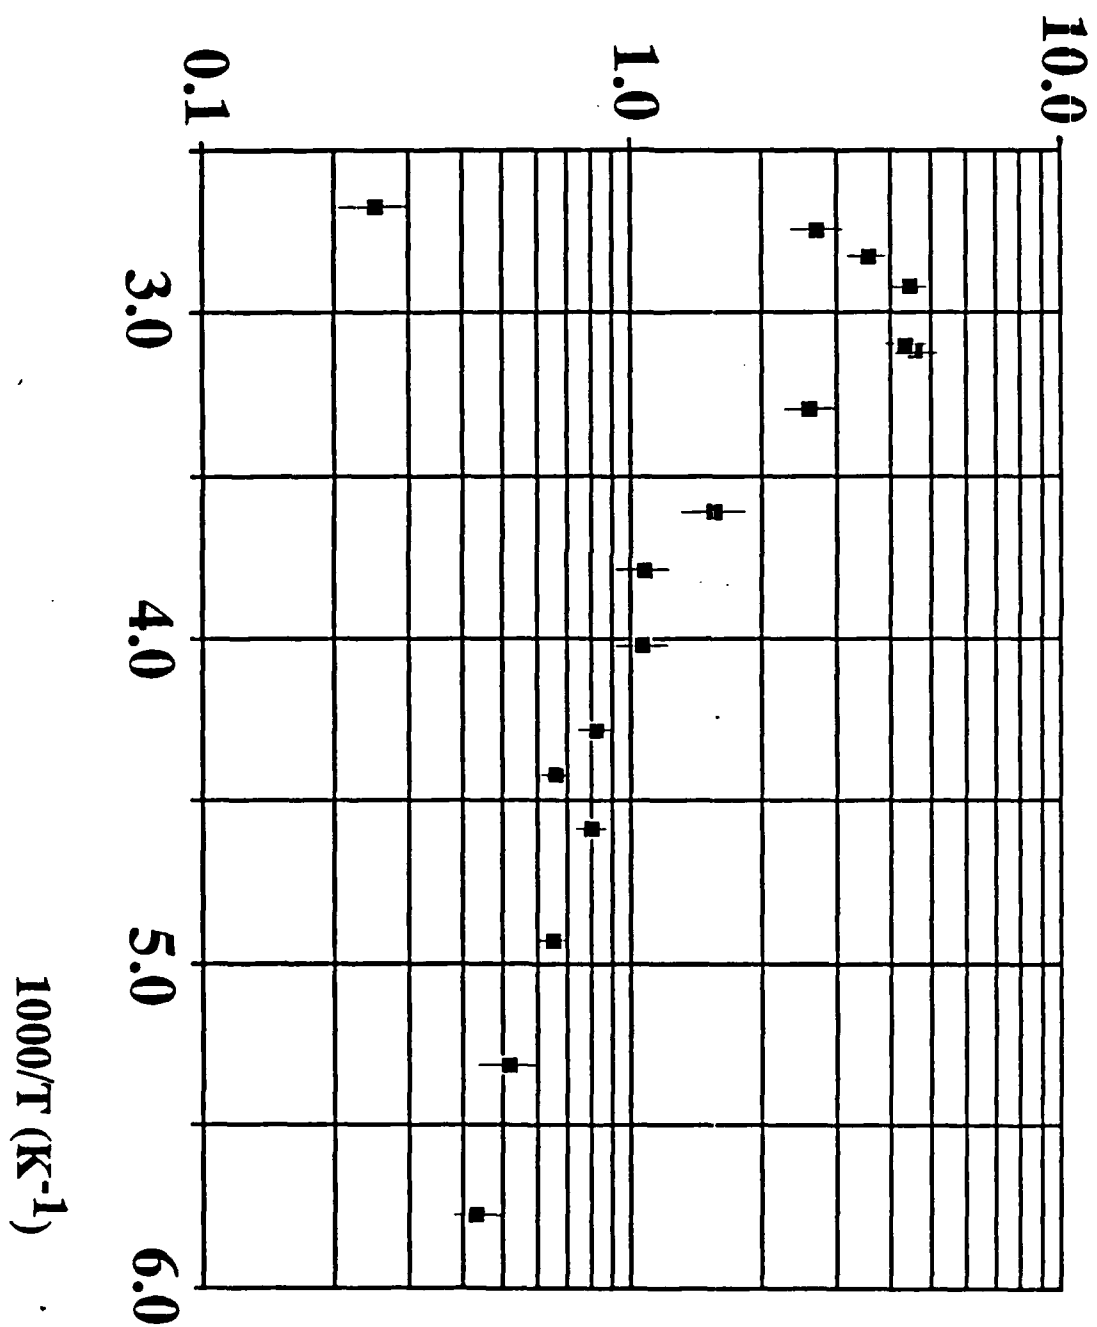

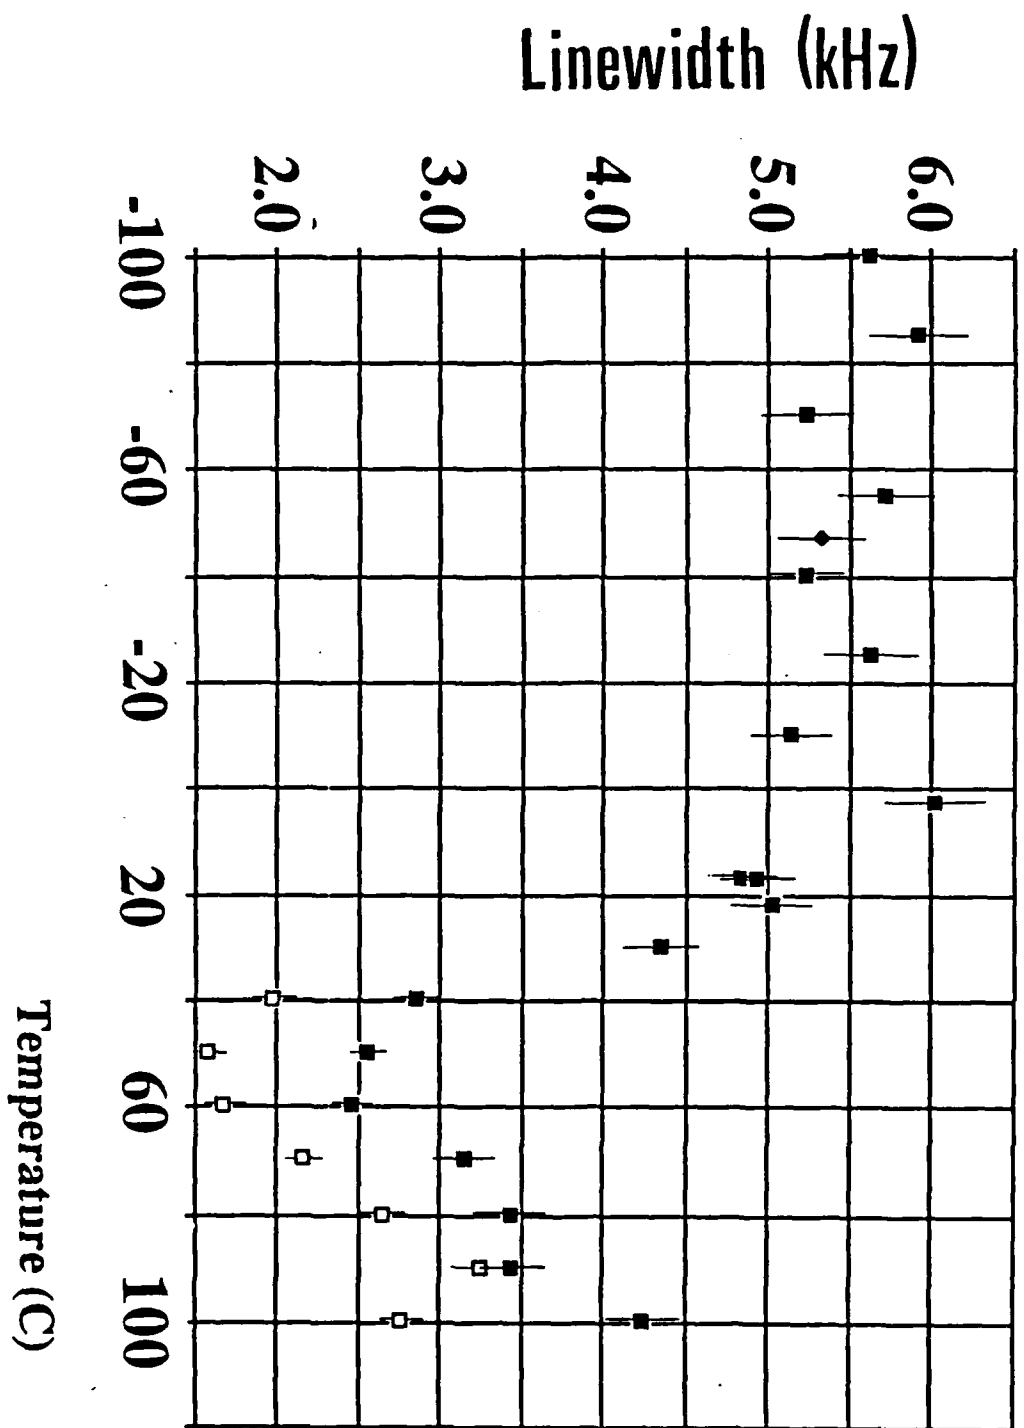

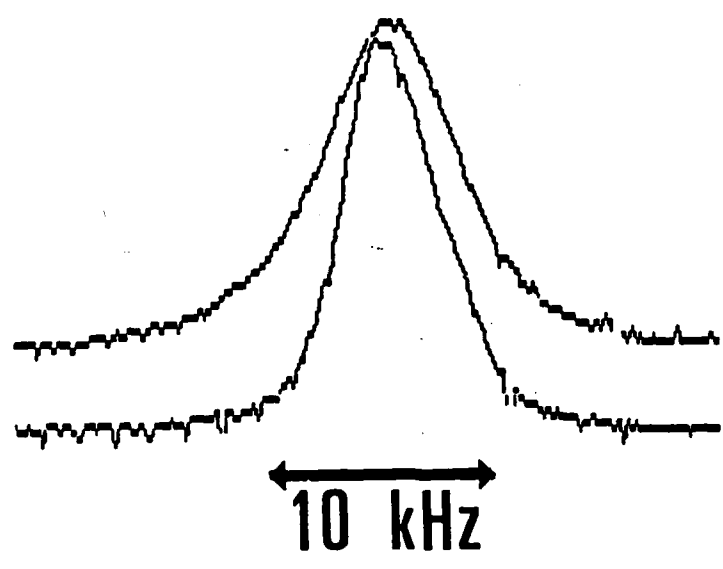

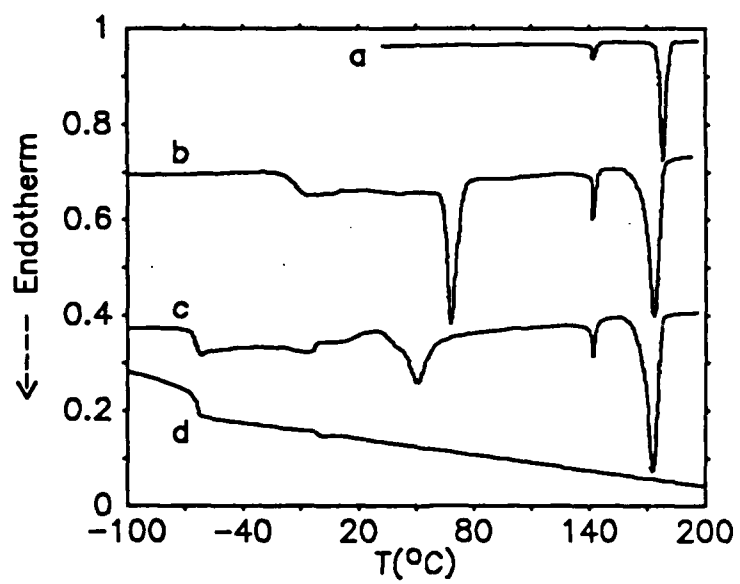

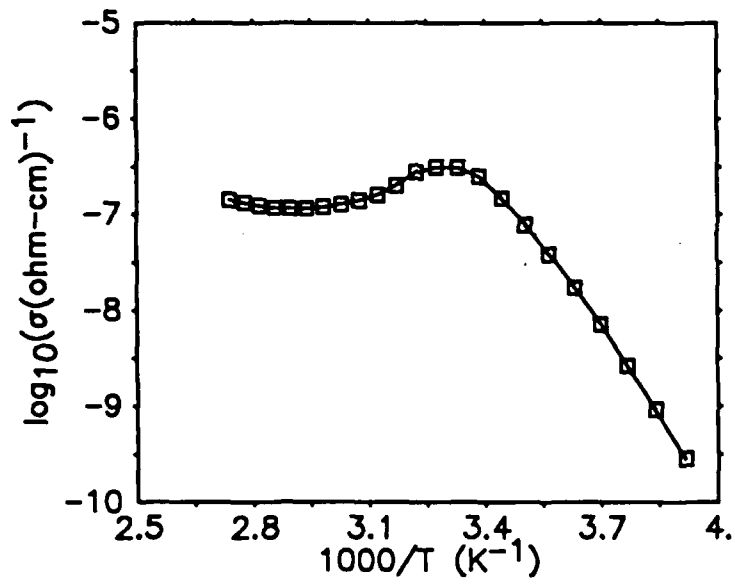


Fig. 7

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code L52 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1

ABSTRACTS DISTRIBUTION LIST, 359/627

Dr. Stanislaw Szpak
Naval Ocean Systems Center
Code 633, Bayside
San Diego, California 95152

Dr. Gregory Farrington
Department of Materials Science
and Engineering
University of Pennsylvania
Philadelphia, Pennsylvania 19104

~~Dr. John Fontanella
Department of Physics
U.S. Naval Academy
Annapolis, Maryland 21402-5062~~

Dr. Micha Tomkiewicz
Department of Physics
Brooklyn College
Brooklyn, New York 11210

Dr. Lesser Blum
Department of Physics
University of Puerto Rico
Rio Piedras, Puerto Rico 00931

Dr. Joseph Gordon, II
IBM Corporation
5600 Cottle Road
San Jose, California 95193

Dr. Joel Harris
Department of Chemistry
University of Utah
Salt Lake City, Utah 84112

Dr. J. O. Thomas
University of Uppsala
Institute of Chemistry
Box 531 Baltimore, Maryland 21218
S-751 21 Uppsala, Sweden

Dr. John Owen
Department of Chemistry and
Applied Chemistry
University of Salford
Salford M5 4WT UNITED KINGDOM

Dr. O. Staffsudd
Department of Electrical Engineering
University of California
Los Angeles, California 90024

Dr. Boone Owens
Department of Chemical Engineering
and Materials Science
University of Minnesota
Minneapolis, Minnesota 55455

Dr. Johann A. Joebstl
USA Mobility Equipment R&D Command
DRDME-EC
Fort Belvoir, Virginia 22060

Dr. Albert R. Landgrebe
U.S. Department of Energy
M.S. 6B025 Forrestal Building
Washington, D.C. 20595

Dr. J. J. Brophy
Department of Physics
University of Utah
Salt Lake City, Utah 84112

Dr. Charles Martin
Department of Chemistry
Texas A&M University
College Station, Texas 77843

Dr. Milos Novotny
Department of Chemistry
Indiana University
Bloomington, Indiana 47405

Dr. Mark A. McHugh
Department of Chemical Engineering
The Johns Hopkins University
Baltimore, Maryland 21218

Dr. D. E. Irish
Department of Chemistry
University of Waterloo
Waterloo, Ontario, Canada
N2L 3G1

DL/1113/87/2

ABSTRACTS DISTRIBUTION LIST, 359/627

Dr. Martin Fleischmann
Department of Chemistry
University of Southampton
Southampton SO9 5H UNITED KINGDOM

Dr. Alan Bewick
Department of Chemistry
The University of Southampton
Southampton, SO9 5NH UNITED KINGDOM

Dr. John Wilkes
Department of the Air Force
United States Air Force Academy
Colorado Springs, Colorado 80840-6528

Dr. Edward Fletcher
Department of Mechanical Engineering
University of Minnesota
Minneapolis, Minnesota 55455

Dr. R. A. Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. Bruce Dunn
Department of Engineering &
Applied Science
University of California
Los Angeles, California 90024

Dr. Janet Osteryoung
Department of Chemistry
State University of New York
Buffalo, New York 14214

Dr. Elton Cairns
Energy & Environment Division
Lawrence Berkeley Laboratory
University of California
Berkeley, California 94720

Dr. A. J. Bard
Department of Chemistry
University of Texas
Austin, Texas 78712

Dr. Richard Pollard
Department of Chemical Engineering
University of Houston
Houston, Texas 77004

Dr. Steven Greenbaum
Department of Physics and Astronomy
Hunter College
695 Park Avenue
New York, New York 10021

Dr. M. Philpott
IBM Research Division
Mail Stop K 33/801
San Jose, California 95130-6099

Dr. Donald Sandstrom
Boeing Aerospace Co.
P.O. Box 3999
Seattle, Washington 98124

Dr. Martha Greenblatt
Department of Chemistry, P.O. Box 939
Rutgers University
Piscataway, New Jersey 08855-0939

Mr. James R. Moden
Naval Underwater Systems Center
Code 3632
Newport, Rhode Island 02840

Dr. Anthony Sammells
Eltron Research Inc.
4260 Westbrook Drive, Suite 111
Aurora, Illinois 60505

Dr. D. Rolison
Naval Research Laboratory
Code 6171
Washington, D.C. 20375-5000

Dr. C. A. Angell
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907

Dr. D. F. Shriver
Department of Chemistry
Northwestern University
Evanston, Illinois 60201

Dr. Thomas Davis
Polymers Division
National Bureau of Standards
Gaithersburg, Maryland 20899

ABSTRACTS DISTRIBUTION LIST, 359/627

Dr. Manfred Breiter
Institut für Technische Elektrochemie
Technischen Universität Wien
9 Getreidemarkt, 1160 Wien
AUSTRIA

Dr. E. Yeager
Department of Chemistry
Case Western Reserve University
Cleveland, Ohio 44106

Dr. R. Sutula
The Electrochemistry Branch
Naval Surface Weapons Center
Silver Spring, Maryland 20910

Dr. R. A. Marcus
Department of Chemistry
California Institute of Technology
Pasadena, California 91125

Dr. J. J. Auborn
AT&T Bell Laboratories
600 Mountain Avenue
Murray Hill, New Jersey 07974

Dr. M. S. Wrighton
Chemistry Department
Massachusetts Institute
of Technology
Cambridge, Massachusetts 02139

Dr. B. Stanley Pons
Department of Chemistry
University of Utah
Salt Lake City, Utah 84112

Dr. Bernard Spielvogel
U.S. Army Research Office
P.O. Box 12211
Research Triangle Park, NC 27709

Dr. Mel Miles
Code 3852
Naval Weapons Center
China Lake, California 93555

Dr. P. P. Schmidt
Department of Chemistry
Oakland University
Rochester, Michigan 48063

Dr. Roger Belt
Litton Industries Inc.
Airtron Division
Morris Plains, NJ 07950

Dr. Ulrich Stimming
Department of Chemical Engineering
Columbia University
New York, NY 10027

Dr. Royce W. Murray
Department of Chemistry
University of North Carolina
Chapel Hill, North Carolina 27514

Dr. Michael J. Weaver
Department of Chemistry
Purdue University
West Lafayette, Indiana 47907

Dr. R. David Rauh
EIC Laboratories, Inc.
Norwood, Massachusetts 02062

Dr. Edward M. Eyring
Department of Chemistry
University of Utah
Salt Lake City, UT 84112

Dr. M. M. Nicholson
Electronics Research Center
Rockwell International
3370 Miraloma Avenue
Anaheim, California

Dr. Nathan Lewis
Department of Chemistry
Stanford University
Stanford, California 94305

Dr. Hector D. Abruna
Department of Chemistry
Cornell University
Ithaca, New York 14853

Dr. A. B. P. Lever
Chemistry Department
York University
Downsview, Ontario M3J 1P3

DL/1113/87/2

ABSTRACTS DISTRIBUTION LIST, 359/627

Dr. Henry S. White
Department of Chemical Engineering
and Materials Science
151 Amundson Hall
421 Washington Avenue, S.E.
Minneapolis, Minnesota 55455

Dr. Daniel A. Buttry
Department of Chemistry
University of Wyoming
Laramie, Wyoming 82071

Dr. W. R. Fawcett
Department of Chemistry
University of California
Davis, California 95616

Dr. Peter M. Blonsky
Eveready Battery Company, Inc.
25225 Detroit Road, P.O. Box 45035
Westlake, Ohio 44145

END

9-87

Dtic