

AD-A193 287


EFFECT OF THERMAL TREATMENT ON THE MECHANICAL AND
TOUGHNESS PROPERTIES OF (U) NAVAL SURFACE WEAPONS
CENTER SILVER SPRING MD D F HASSON ET AL 31 JAN 87
NSWC/TR-86-72 F/G 11/4

1/1

UNCLASSIFIED

NL



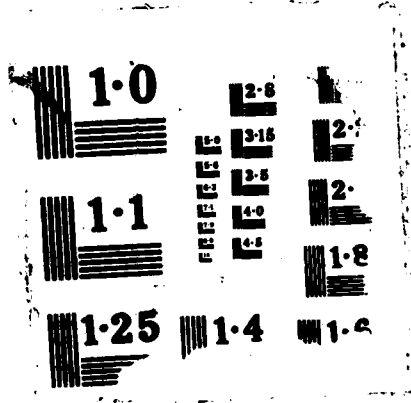

NSWC TR 86-72

AD-A193 207

EFFECT OF THERMAL TREATMENT ON THE MECHANICAL AND TOUGHNESS PROPERTIES OF EXTRUDED SiC_w /ALUMINUM 6061 METAL MATRIX COMPOSITE

BY D. F. HASSON S. M. HOOVER C. R. CROWE

RESEARCH AND TECHNOLOGY DEPARTMENT

31 JANUARY 1987

Approved for public release; distribution is unlimited.

DTIC
ELECTE
S APR 13 1988 D
aE



NAVAL SURFACE WEAPONS CENTER

Dahlgren, Virginia 22448-5000 • Silver Spring, Maryland 20903-5000

88 4 12 066

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

1a REPORT SECURITY CLASSIFICATION UNCLASSIFIED			1b RESTRICTIVE MARKINGS		
2a SECURITY CLASSIFICATION AUTHORITY			3 DISTRIBUTION / AVAILABILITY OF REPORT Approved for public release; distribution is unlimited.		
2b DECLASSIFICATION / DOWNGRADING SCHEDULE			4 PERFORMING ORGANIZATION REPORT NUMBER(S) NSWC TR 86-72		
4 PERFORMING ORGANIZATION REPORT NUMBER(S) NSWC TR 86-72			5 MONITORING ORGANIZATION REPORT NUMBER(S)		
6a NAME OF PERFORMING ORGANIZATION Naval Surface Weapons Center		6b OFFICE SYMBOL (If applicable) Code R32	7a NAME OF MONITORING ORGANIZATION		
6c ADDRESS (City, State, and ZIP Code) 10901 New Hampshire Avenue Silver Spring, Maryland 20903-5000			7b ADDRESS (City, State, and ZIP Code)		
8a NAME OF FUNDING / SPONSORING ORGANIZATION		8b OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER		
8c ADDRESS (City, State, and ZIP Code)			10. SOURCE OF FUNDING NUMBERS		
PROGRAM ELEMENT NO. 62761N		PROJECT NO. SF61544	TASK NO. 2R32BF	WORK UNIT ACCESSION NO.	
11 TITLE (Include Security Classification) Effect of Thermal Treatment on the Mechanical and Toughness Properties of Extruded Sic_w/Aluminum 6061 Metal Matrix Composites					
12 PERSONAL AUTHOR(S) Hasson, D. F.; Hoover, S. M.; Crowe, C. R.					
13a TYPE OF REPORT Final		13b TIME COVERED FROM _____ TO _____	14. DATE OF REPORT (Year, Month, Day) 1987, January, 31		15 PAGE COUNT 25
16 SUPPLEMENTARY NOTATION					
17 COSATI CODES			18 SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB-GROUP	Mechanical Strength Properties, Toughness Behaviors		
11	04		Thermal Treatments		
11	06	01	Charpy V-Notch, (CVN). Sic _w /Aluminum		
19. ABSTRACT (Continue on reverse if necessary and identify by block number) Mechanical, instrumented Charpy V-notch (CVN) energy and plane strain fracture toughness properties of Sic whisker reinforced 6061 aluminum metal matrix composite material from an extruded tube have been determined. The effect of thermal treatment and orientation have been studied. The mechanical strength properties are higher than wrought Al 6061 in the T6 condition. CVN energy values, however, were reduced by an order of magnitude. K _{IC} fracture toughness of the as-received, T6 and degassed + T6 thermal treatments were 50% of the wrought Al 6061 alloy. The effect of orientation showed that the orientation with the least amount of Sic whisker in the crack plane (i.e. greatest mean free path between reinforcements) yields the highest toughness value. <i>See ref. 1</i>					
20 DISTRIBUTION / AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS			21. ABSTRACT SECURITY CLASSIFICATION UNCLASSIFIED		
22a NAME OF RESPONSIBLE INDIVIDUAL Scott M. Hoover			22b TELEPHONE (Include Area Code) (202)394-2527		22c OFFICE SYMBOL Code R32

DD FORM 1473, 84 MAR

83 APR edition may be used until exhausted
All other editions are obsolete

SECURITY CLASSIFICATION OF THIS PAGE

★ U.S. Government Printing Office: 1986-607-044


UNCLASSIFIED

FOREWORD

The authors express their appreciation to Messrs. W. Willard and R. Gray for the fracture testing, Ensign M. Rennie for the instrumented Charpy V-notch testing, and Messrs. W. Umlandt and F. W. Rider for laboratory support. The authors also wish to acknowledge Mr. J. E. Tydings for supplying the tube material and Mr. Marlin Kinna, NAVSEA 06ZR, for financial assistance.

Approved by:

Jack R. Dixon
 JACK R. DIXON, Head
 Materials Division

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	
	

CONTENTS

<u>Chapter</u>		<u>Page</u>
1	INTRODUCTION	1
2	EXPERIMENTAL PROCEDURE	3
	MATERIALS	3
	THERMAL TREATMENTS	4
	MECHANICAL TESTS	6
	TOUGHNESS TESTS	6
	FRACTOGRAPHY	6
3	RESULTS AND DISCUSSION	9
	MECHANICAL PROPERTIES	9
	FRACTOGRAPHY	10
	TOUGHNESS BEHAVIOR	13
4	CONCLUSIONS	17
	REFERENCES	19
	DISTRIBUTION	(1)

ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
1	MICROSTRUCTURE OF SiC _w /Al 6061 EXTRUDED TUBE MATERIAL	5
2	ORIENTATION OF SPECIMENS FROM EXTRUDED TUBE	7
3	EXAMPLE OF NONBONDED REGION IN BASE OF "FISHEYE" ON FRACTURE SURFACE: (A) 4 μ m, AND (B) 20 μ m	11
4	FRACTURE MORPHOLOGY CAUSED BY DECOHESION AT ALUMINUM GRAIN BOUNDARIES: (A) SEM MORPHOLOGY, AND (B) TRANSMISSION ELECTRON MICROGRAPH SHOWING RELATIONSHIP OF SiC WHISKERS TO ALUMINUM GRAIN BOUNDARIES	12
5	INSTRUMENTED CHARPY V-NOTCH LOAD AND ENERGY AGAINST TIME OUTPUTS FOR L-C ORIENTATION SiC _w /Al 6061 EXTRUDED TUBE MATERIALS AT 0.13 MSEC ⁻¹ : (A) DEGASSED, AND (B) DEGASSED + T6	14

TABLES

<u>Table</u>		<u>Page</u>
1	CHEMICAL ANALYSES (WT%) OF WROUGHT A1 6061 AND COMPOSITE SiC _w /A1 6061 FROM EXTRUDED TUBE	3
2	DESCRIPTION OF THERMAL TREATMENTS TO EXTRUDED TUBE MATERIALS	4
3	MECHANICAL PROPERTIES OF LONGITUDINAL ORIENTATION SPECIMENS FROM EXTRUDED TUBE MATERIAL	9
4	EFFECT OF THERMAL TREATMENT ON THE TOUGHNESS BEHAVIOR OF SiC _w /A1 6061 COMPOSITE MATERIAL (SPECIMEN ORIENTATION L-C)	13
5	EFFECT OF ORIENTATION ON THE K _{IC} FRACTURE TOUGHNESS BEHAVIOR OF DEGASSED + T6 SPECIMENS FROM EXTRUDED TUBE	15

CHAPTER 1

INTRODUCTION

Discontinuous silicon carbide/aluminum alloy (SiC/Al) metal matrix composites (MMCs) have exhibited improved physical and mechanical properties as compared to the wrought properties of the matrix alloy. These improved properties include high specific modulus, high creep strength, high fatigue resistance, low thermal expansion, and good thermal stability.¹⁻⁹ The SiC/Al composite can also be worked using standard metallurgical processing so it is inexpensive to produce compared to other MMC systems. The tensile ductility and fracture properties of the composite reported to date, however, are less than wrought alloy properties.^{1, 10-15} The tensile ductility has been improved by control of process parameters, but there has been little improvement in fracture toughness. The objective of this study is to improve fracture toughness by thermal treatment. Orientation effects on fracture toughness are also reported.

CHAPTER 2
EXPERIMENTAL PROCEDURE

MATERIALS

The materials were 20 vol% SiC_w/Al 6061 composite from a 31.8 mm wall thickness, 320 mm diameter extruded cylinder. The SiC used to form the composite was a mixture of fine whiskers and particles with original whisker content of about 80%. The whiskers are B-SiC with diameters ranging from 0.2 to 1.0 μm and original lengths up to 50 μm. The whiskers were blended with commercially available, -325 mesh, inert gas atomized Al 6061 powders. The composite was formed by cold compaction followed by hot pressing at temperatures above the solidus of the matrix to form as-pressed billet material. The billet was then extruded to form the tube.

Chemical analysis of the composite is given in Table 1. Chemical analysis for wrought Al 6061 is given for comparison.

**TABLE 1. CHEMICAL ANALYSES (wt%) OF
WROUGHT Al 6061 AND COMPOSITE
SiC_w/Al 6061 FROM EXTRUDED TUBE**

ELEMENT	WROUGHT Al 6061	COMPOSITE SiC _w /Al 6061
Mg	0.82	0.66
Si	0.68	—
Cr	0.16	0.18
Cu	0.18	0.39
Fe	0.44	0.65
Mn	0.06	0.08
Ni	0.01	0.01
Zn	0.11	0.03
Ti	0.01	0.03
SiC	—	25.41
C	—	7.61
O	—	0.4530
H	—	0.0005
N	—	0.0871
Al	REMAINDER	REMAINDER

The microstructure of the material is shown in Figure 1. Fibers are generally aligned in the extrusion direction. The microstructure of the composite also shows that most of the whiskers were fragmented during fabrication of the cylinder.

THERMAL TREATMENTS

Specimens were cut from the cylinder and thermally treated as described in Table 2 to provide specimens of as-received, T6, degassed, and degassed followed by a T6 thermal treatment.

TABLE 2. DESCRIPTION OF THERMAL TREATMENTS TO EXTRUDED TUBE MATERIALS

CONDITION	THERMAL TREATMENT
AS-RECEIVED T6	NONE PRIOR TO TESTING SOLUTION TREATED AT 527°C FOR 1 h; COLD WATER QUENCHED; THEN PRECIPITATION HARDENED AT 177°C FOR 8 h FOLLOWED BY AIR COOLED
DEGASSED	HEATED TO 500°C FOR 48 h IN A 25 m TORR VACUUM. SPECIMEN ALLOWED TO COOL <i>IN VACUO</i>.
DEGASSED + T6	DEGAS THERMAL TREATMENT WAS USED, THEN T6 THERMAL TREATMENT APPLIED

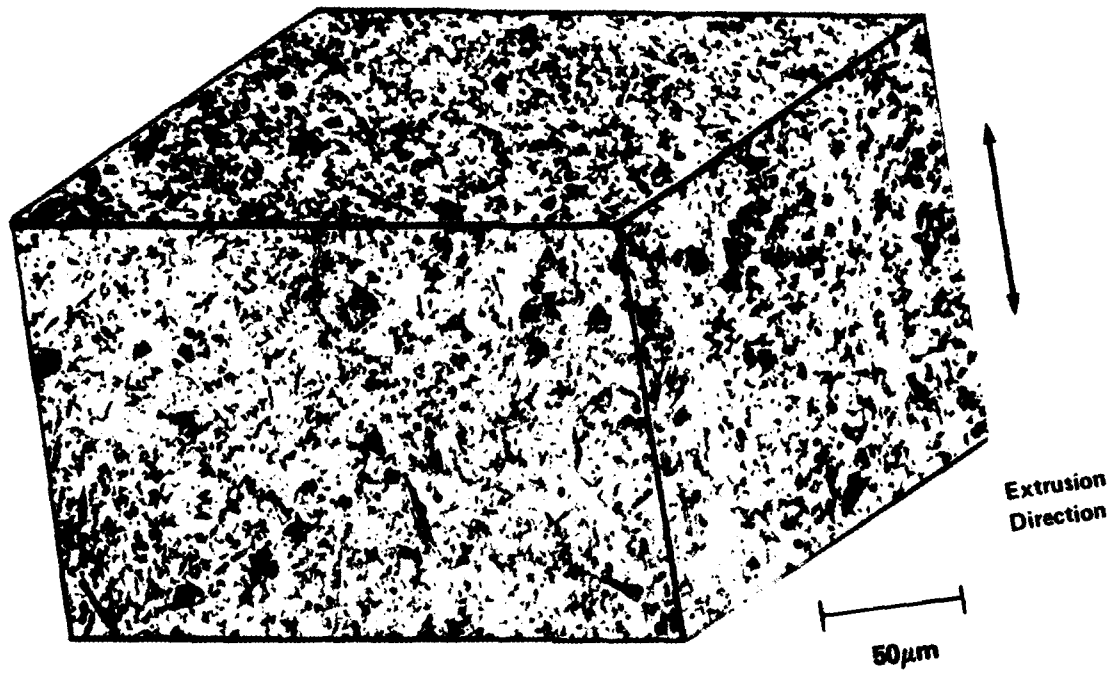


FIGURE 1. MICROSTRUCTURE OF SiC_w/Al 6061 EXTRUDED TUBE MATERIAL

MECHANICAL TESTS

Duplicate longitudinal orientation,¹⁶ 4.1 mm diameter tensile test specimens were fabricated and tested at room temperature to obtain modulus of elasticity, 0.2% offset yield stress, ultimate tensile stress, and percent elongation. Specimen orientations are shown in Figure 2. Duplicate 12.8 mm as-received specimens were also tested to determine a possible volume effect. Also Rockwell-B Scale (HRB) measurements were made on the materials.

TOUGHNESS TESTS

Charpy V-notch (CVN) specimens were prepared from all thermal treatments in L-C orientation. Triplicate specimens were tested at room temperature in an instrumented Charpy tester.

K_{IC} fracture toughness testing was performed on duplicate 1/2T compact tensile specimens from all thermally treated materials in the L-C orientation. Degassed + T6 specimens were also tested in the R-L and C-L orientations. The testing and data analysis conformed to ASTM E399 procedures¹⁷ except the specimens were not fatigue precracked. Data from a separate study on the effect of notch acuity¹⁸ was used to select a valid notch root radius. The study showed that a valid K_{IC} is obtained with a notch root radius of less than 80 μm . The notch radius for the results reported here was 74 μm .

FRACTOGRAPHY

Stereo pair Scanning Electron Microscopy (SEM) along with Energy Dispersive X-ray Analysis (EDAX) fractography was performed on representative fracture surfaces.

The dimple, height h , measurements were made from SEM stereo pairs using the relation

$$h = \frac{P}{2M} \left(\sin \frac{\phi}{2} \right)^{-1} \quad (1)$$

where P is the parallax, M is the magnification, and ϕ is the tilt angle between the stereo pairs. Parallax is measured as the difference in distance between any two identifiable image points measured on one photograph, and that same distance measured on the other photograph of the stereo pair.

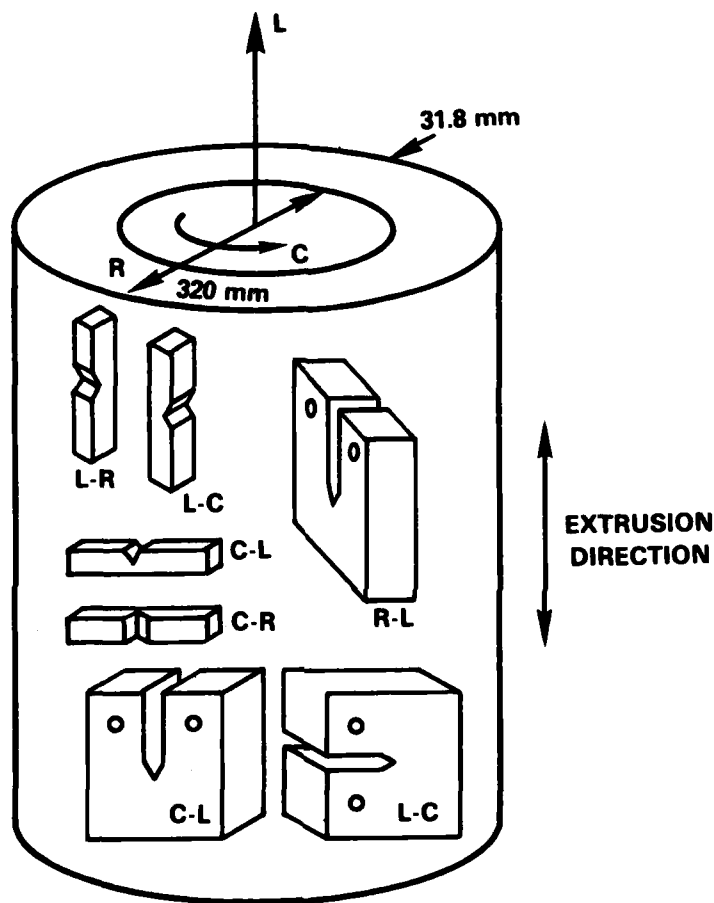


FIGURE 2. ORIENTATION OF SPECIMENS FROM EXTRUDED TUBE

CHAPTER 3

RESULTS AND DISCUSSION

MECHANICAL PROPERTIES

The mechanical properties of the various thermally treated longitudinal orientation specimens are given in Table 3. Also included are reference values¹⁹ for wrought Al 6061 in the T6 condition. Comparison of Al 6061-T6 and SiC_w/Al 6061-T6 properties shows significant increases in modulus, yield stress, and ultimate stress due to the addition of the SiC whiskers. Ductility, however, is less in the SiC_w/Al 6061-T6 materials.

TABLE 3. MECHANICAL PROPERTIES OF LONGITUDINAL ORIENTATION SPECIMENS FROM EXTRUDED TUBE MATERIAL

CONDITION	MODULUS (GPa)	0.2 OFFSET YIELD STRESS (MPa)	ULTIMATE TENSILE STRESS (MPa)	ELONGATION IN 4D (%)	HRB
AS-RECEIVED	108.4	335.4	489.7	3.4	64.5
	108.6*	332.0*	463.0*	3.4*	
T6	103.1	375.4	517.8	3.0	85.0
DEGASSED	105.8	175.1	365.4	5.0	55.7
DEGASSED + T6	107.9	374.4	520.6	2.7	88.6
Al 6061-T6**	69.0	275.8	310.3	17.0	91.0

*12.8 mm DIAMETER SPECIMEN; ALL OTHER 4.1 mm DIAMETER.

**DATA FROM REFERENCE 19.

The extruded tube (as-received material) was to be delivered in T6 condition. The slightly lower values of yield stress and HRB can be attributed to overaging caused by lower cooling rates in the extruded tube during quenching following aging. Also, in the as-received material, specimens of large diameter were tested to determine if there is a material sample volume effect. The results were identical to the subsized tensile data.

Degassing the material, which amounts to an anneal, reduced the yield and ultimate stresses by 53% with a slight improvement of 1.6% in ductility (i.e. percent elongation). Reheat treating the degassed material to T6 condition (degassed + T6), as shown in Table 3, restores the yield and ultimate

stresses exactly to the T6 level. This indicates that the concentration of magnesium was not significantly decreased in the degassing heat treatment. Vacuum degassing at higher temperatures or longer times could result in the loss of magnesium and subsequent loss of strength from precipitation hardening.

It should be noted that the T6 and the degassed + T6 thermal treatments in Table 2 are the standard thermal treatments for wrought Al 6061 alloys. The effect of the presence of the SiC whiskers on the solution pretreatment and aging processes has not been extensively studied. Harrigan et al.²⁰ has presented results for a 30 vol% SiC particulate (SiC_p)/Al 6061 alloy which indicated that solution treatment similar to those used for wrought Al 6061 are satisfactory, while aging response is accelerated in the composite SiC_p/Al 6061 alloy. Similar behavior is described by Papazian²¹ for whisker material. One could then speculate that in the present treatments a slight degree of overaging might have occurred, and the yield, ultimate stresses, and hardness might be higher with slightly reduced aging time.

FRACTOGRAPHY

Observations of fracture surfaces in the SEM revealed five distinct morphological features. These features, which varied widely in frequency of occurrence on the fracture surface and in decreasing frequency of observation, are:

1. Dimples--Most of the fracture surface consisted of fine and equiaxed dimples of uniform size. Embedded in the base of approximately 50% of the dimples is an SiC particle tip which, according to Arsenault,²² is covered with a coating of Al matrix.

Quantitative measurements of the mean dimple diameter and height measured from stereo pairs shows that the mean dimple diameter is 1.78 μm , and the mean dimple height is 0.95 μm . Thus, the dimple is slightly elongated in the tensile axis direction.

2. Inclusions--Both iron-rich and chromium-rich inclusions were observed.
3. Nonbonded regions--Regions of nonbonded matrix material were observed in the extruded tube material. Figure 3(A) shows an example where it appears that SiC was pressed into the matrix material but consolidation apparently did not occur during fabrication. These nonbonded regions appeared either coplanar with the plan of fracture or in the base of the so-called "fisheyes" [Figure 3(B)].
4. Regions of non-infiltration--Areas which lacked matrix material were rare. In older material, these features were more numerous but improvements in mixing and consolidation processing greatly reduced the frequency of these defects.
5. Decohesion at aluminum grain boundaries--Occasional observation of decohesion at aluminum grain boundaries was observed. The resulting morphology is shown in Figure 4(A). The triple point void shown in Figure 4(A) is not always present, but the morphology is distinguished from normal dimples by the location of SiC at the edge of the dimple. The relative location of the boundaries and the SiC particles can be compared with the transmission electron micrograph of Figure 4(B).

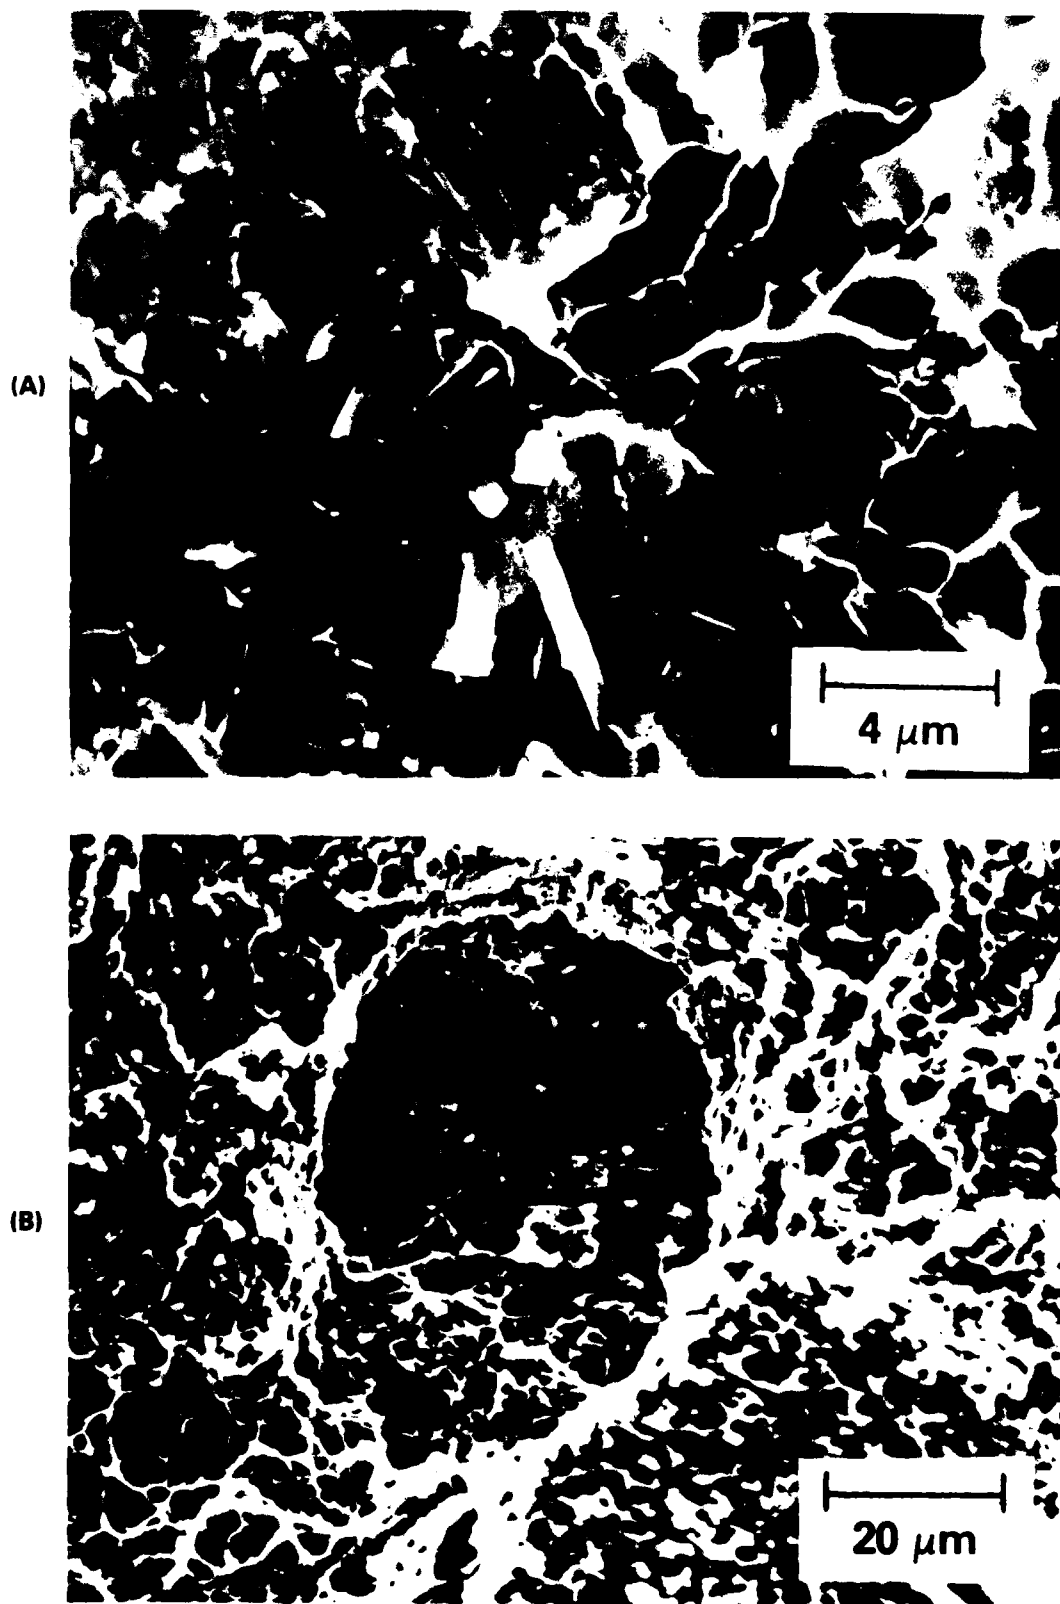


FIGURE 3. EXAMPLE OF NONBONDED REGION IN BASE OF "FISHEYE" ON FRACTURE SURFACE:
(A) 40 μm , AND (B) 20 μm

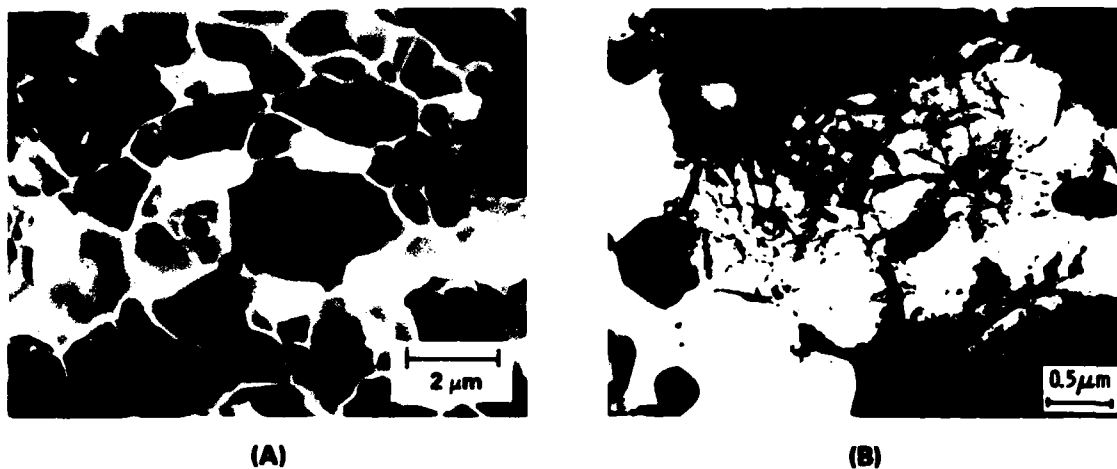


FIGURE 4. FRACTURE MORPHOLOGY CAUSED BY DECOHESION AT ALUMINUM GRAIN BOUNDARIES: (A) SEM MORPHOLOGY, AND (B) TRANSMISSION ELECTRON MICROGRAPH SHOWING RELATIONSHIP OF SiC WHISKERS TO ALUMINUM GRAIN BOUNDARIES

TOUGHNESS BEHAVIOR

The effect of thermal treatment on the toughness behavior of SiC_w/Al 6061 composite material is given in Table 4. Specimen orientation was L-C. The CVN energy values are nearly the same for all the thermal treatments studied. The values are at least an order of magnitude lower than the wrought Al 6061 alloy in the T6 condition. Degassing the composite material did give the highest absorbed energy value of 1.6J compared to 0.5J for the other thermal treatments. Also macrofractographic examination revealed about 10% shear on the degassed specimens, compared to zero for the others. The instrumented Charpy traces, shown in Figure 5(A) and 5(B), further illustrate the impact energy value differences. The load-time trace for the degassed material, Figure 5(A), exhibits general yield, while the degassed + T6 shows a classic brittle behavior. A derived dynamic stress intensity value, K_{I_d} , from this test was 19.1 MPam^{1/2}. Similar results are reported by Strife and Prewo.²³

TABLE 4. EFFECT OF THERMAL TREATMENT ON THE TOUGHNESS BEHAVIOR OF SiC_w/Al 6061 COMPOSITE MATERIAL (SPECIMEN ORIENTATION L-C)

THERMAL TREATMENT	CVN ENERGY (J)	FRACTURE TOUGHNESS, K_{Ic} (MPam ^{1/2})
AS-RECEIVED	0.5	19.5
T6	0.6	23.4
DEGASSED	1.6	18.9*
DEGASSED + T6	0.6	22.4
Al 6061-T6	23.1**	36.8†

* K_{Ic} VALUE BASED ON MAXIMUM LOAD.

**TESTED BY DFH ON STANDARD CVN TESTER.

†CALCULATED FROM G_{Ic} VALUE OF REFERENCE 24.

The K_{Ic} fracture toughness values in Table 4 shows similar results to the Charpy energy values for the various thermal treatments. A valid K_{Ic} value for the degassed material, however, could not be determined because the ratio of P_{max} to p_Q significantly exceeded 1.10. This behavior requires an elastic-plastic J_{Ic} test to determine the crack initiation energy. The value of 18.9 MPam^{1/2} for the degassed material in Table 4 was calculated using P_{max} and thus is conservative. The level of all K_{Ic} values for the composite are about 50% of the K_{Ic} value of 36.8 MPam^{1/2} of wrought Al 6061 alloy in the T6 condition. This

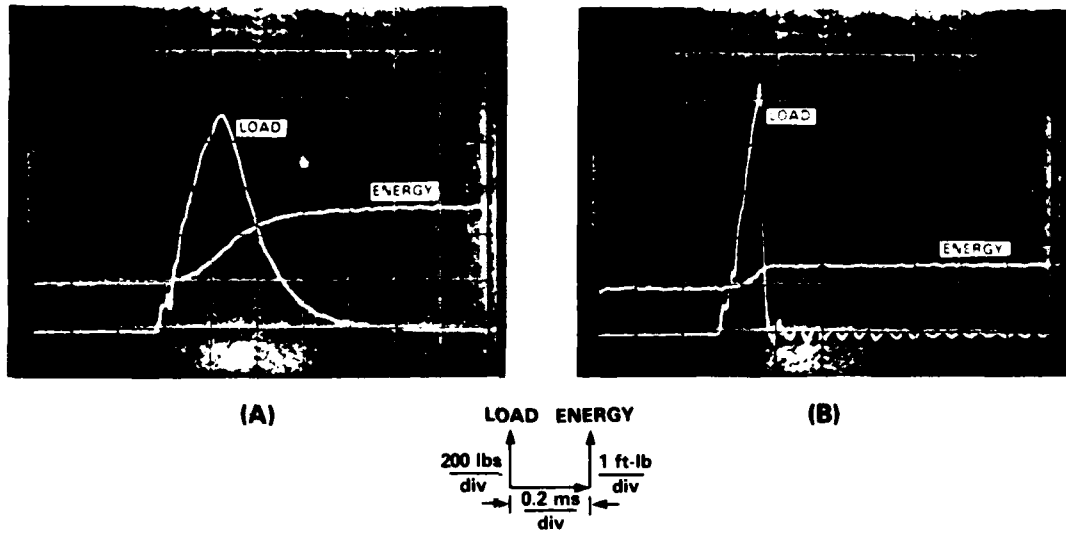


FIGURE 5. INSTRUMENTED CHARPY V-NOTCH LOAD AND ENERGY AGAINST TIME OUTPUTS FOR L-C ORIENTATION SiC_w/AI 6061 EXTRUDED TUBE MATERIALS AT 0.13 msec⁻¹: (A) DEGASSED, AND (B) DEGASSED + T6

value was calculated from the G_{IC} value of Kambour and Miller.²⁴ It is noted that Kambour and Millers' K_{IC} value for Al 6061-T6 is in the range of values reported by Kaufman²⁵ of 30.8 to 50.47 MPam^{1/2}. The addition of the SiC whiskers, therefore, is not completely deleterious to the fracture toughness of the Al 6061 alloy as might be expected from the high volume fraction of the SiC.

The effect of orientation on the K_{IC} fracture toughness of degassed + T6 composite material is given in Table 5. The orientation of highest toughness is L-C, as also found by Crowe and Gray.¹³ It is speculated that the L-C orientation is toughest because it has the least amount of projected area of SiC whiskers in the crack plane (i.e. the mean free path between reinforcements is the greatest).

TABLE 5. EFFECT OF ORIENTATION ON THE K_{IC} FRACTURE TOUGHNESS BEHAVIOR OF DEGASSED + T6 SPECIMENS FROM EXTRUDED TUBE

ORIENTATION	FRACTURE TOUGHNESS, K_{IC} (MPam^{1/2})
L-C	22.4
R-L	14.0
C-L	17.6

Furthermore, SEM fractography indicates the fracture occurs by a ductile mechanism with plastic deformation localized adjacent to the crack tip. This produces a fracture surface consisting of fine dimples, as mentioned previously. The size of the dimples (2 μ m) is on the order of the size of several microstructural features such as the subgrain size of the Al matrix, the mean particle diameter, and the mean particle spacing. Stereo pair SEM reveals that the dimples are nearly spherical, but slightly elongated parallel to the load axis. These observations suggest that a critical strain criterion at the crack tip may control fracture. The small-scale yielding observed also suggests that fracture toughness is linked to the microstructure.

McMeeking²⁶ has shown from continuum mechanics that in small-scale yielding fracture, the crack tip opening displacement, σ_t , is related to the stress intensity by the relation

$$\sigma_t = \frac{\alpha K_I}{\sigma_y E} \quad (2)$$

where α is a numerical constant between 0.25 and 1.00. If the fracture mechanism is associated with the nucleation, growth, and coalescence of voids, then the critical crack tip opening displacement, σ_{tIC} , is just twice the mean dimple height, and the plane strain fracture toughness, K_{IC} , is given by

$$K_{IC} = \left(\frac{2\sigma_y E h}{\alpha} \right)^{1/2}. \quad (3)$$

Using tensile data from Table 3 for the as-received specimen, Equation (3) predicts that K_{IC} should range between 8.3 and 16.6 MPam^{1/2} which is in agreement with the present results.

CHAPTER 4

CONCLUSIONS

The following observations were made:

1. Compared to wrought Al 6061 alloy, significant increases in modulus, yield stress, and ultimate tensile stress were observed in as-received and T6 heat treated composite materials which were obtained from an extruded SiC_w/Al tube. Ductility, however, was decreased. The strength properties of the as-received tube material indicated that a T6 condition was not obtained. This was attributed to lower cooling rates following aging in the large extrusion.

2. CVN energy values of the composite material were reduced by an order of magnitude compared to wrought Al 6061 alloy. Thermal treatment has essentially no effect, but for the degassed thermal treatment a general yield behavior was observed in the instrumented Charpy load-time traces.

3. K_{IC} fracture toughness of the as-received, T6, and degassed + T6 thermal treatments was 50% of the wrought Al 6061 alloy.

4. The effect of orientation showed that the orientation with the least amount of SiC whiskers in the crack plane (i.e. greatest mean free path between reinforcements) yields the highest toughness value.

REFERENCES

1. Divecha, A. P.; Crowe, C. R.; and Fishman, S. G., "Properties of a SiC/Al Composite," Failure Modes in Composites IV, edited by Cornie, J. A., and Crossman, F. W., AIME, Warrendale, Pennsylvania, 1978, p. 406.
2. Divecha, A. P.; Fishman, S. G.; and Karmarkar, S. G., Journal of Metals, Vol. 33, No. 12, 1981.
3. Webster, D. A., "Advances in Composite Materials," in Proceedings of the International Conference on Composite Materials, Vol. 2, Paris, France, edited by Bunsell, A. R., Pergamon Press, New York, 1983, p. 1165.
4. Lederick R. J. and Sastry, S. M. L., Materials Science Engineering, Vol. 55, 1982, No. 143.
5. Neih, T. G., Metal Trans., Vol. 15A, 1982, No. 139.
6. Arsenault, R. J., Material Science Engineering, Vol. 64, 1984, p. 171.
7. Crowe, C. R. and Hasson, D. F., "Corrosion Fatigue of SiC/Al MMC in Salt Laden Moist Air," Strength of Metals and Alloys, Vol. 2, edited by Gifkins, R. C., Pergamon Press, New York, p. 859-65.
8. Boorujy, J. R.; Hasson, D. F.; and Crowe, C. R., US Naval Academy, Annapolis, MD, EW-20-83, DTIC ADA134108, 1983.
9. Hasson, D. F.; Crowe, C. R.; Ahern, J. S.; and Cooke, D. C., Failure Mechanisms in High Performance Materials, edited by Early, J. G. and Shives, R., Cambridge University Press, New York, 1985, p. 147.
10. Lagreca, P. D. and Misra, M., Contract Report N60921-M-4538, Martin Marietta Aerospace, Denver, CO, Apr 1983.
11. DeJarnette, H. M.; Divecha, A. P.; and Willard, W. A., Naval Surface Weapons Center, NSWC TR 84-20, Jan 1984.
12. Dolowy, J. F.; Harrigan, W. C.; and Webb, B. A., Phase II Final Report, Contract Report N00824-80-C-5637, Naval Sea Systems Command, Washington, DC, Mar 1983.
13. Crowe, C. R. and Gray, R. J., Failure Mechanisms in High Performance Materials, edited by Early, J. G. and Shives, R., Cambridge University Press, New York, 1985, p. 157.

REFERENCES (Cont.)

14. Harrigan, W. C., in Proceedings of the Sixth Annual Discontinuous Reinforced Aluminum Composite Working Group Meeting, Metal Matrix Composites Information Analysis Center, Santa Barbara, CA, Rep. MMCIA No. 000479, Apr 1984, p. 211.
15. Cox, J. M. and Chellan, D., in Proceedings of the Sixth Annual Discontinuous Reinforced Aluminum Composite Working Group Meeting, Metal Matrix Composites Information Analysis Center, Santa Barbara, CA, Rep. MMCIA No. 000479, Apr 1984, p. 167.
16. Goode, R. J., Materials Research and Standards, MISRA, American Society of Testing Materials, Vol. 12, No. 9, 1972.
17. ASTM Standard E399, 1978 Annual Book of ASTM Standards, Part 10, ASTM Philadelphia, PA, 1978.
18. Crowe, C. R.; Gray, R. A.; and Hasson, D. F., NRL Memo Rpt. 5417, Naval Research Laboratory, Washington, DC, 1985.
19. Metals Handbook, 8th Edition, Vol. 1, "Properties and Selection of Materials," edited by T. Lyman, American Society for Metals, Metals Park, OH, 1961, p. 964.
20. Harrigan, W. C.; Ristow, M. T.; Dolowy, J. F.; and Webb, B. A., in Proceedings of TMS-AIME 112th Annual Meeting, Atlanta, GA, 6-10 Mar 1983 (AIME, Warrendale, PA).
21. Papazian, J. M., in Proceedings of the Sixth Annual Discontinuous Reinforced Aluminum Composite Working Group Meeting, MMCIA Report No. 00479, AIME, Warrendale, PA, Apr 1984, p. 223.
22. Arsenault, R. J. in Proceedings of the Sixth Annual Discontinuous Reinforced Aluminum Composite Working Group Meeting, MMCIA Rpt. No. 00479, AIME, Warrendale, PA, Apr 1984, p. 1.
23. Strife, J. R. and Prewo, K. M., United Technologies Research Center, Report No. R82-916176-1, Dec 1982.
24. Kambour, R. P. and Miller, S., Journal of Materials Science, Vol. 12, 1977, p. 2281.
25. Kaufman, J. G., Fracture Prevention and Control, edited by Hoepfner, D. W., American Society for Metals, Metals Park, OH, 1974, pp. 121-41.
26. McMeeking, R. M., J. Mech. Phys. Solids, Vol. 25, 1977, p. 357.

DISTRIBUTION

	<u>Copies</u>		<u>Copies</u>
Department of the Navy United States Naval Academy Attn: Prof. D. Hasson Office of the Superintendent Mechanical Engineering Dept. Annapolis, MD 21402	10	Defense Technical Information Center Cameron Station Alexandria, VA 22304-6145	12
Naval Research Laboratory Attn: Code 6372, Dr. R. Crowe Engineering Department Washington, DC 20375	10	Library of Congress Attn: Gift and Exchange Div. Washington, DC 20540	4
Office of Naval Research Attn: Code 1131, Dr. S. Fishman 800 N. Quincy St. Arlington, VA 22217	7	Internal Distribution: R32 (S. Hoover) (J. Tydings) (J. Jarus) R33 (R. Sutula) (C. Dacres) (J. McIntyre) R30 E231 E232	10 1 1 1 1 1 2 15
Naval Sea Systems Command Attn: SEA-062R, M. Kinna Washington, DC 20362	1		

END

DATE

FILM

DTIC

2-85