

AD-A210 496

FILE COPY

4

OFFICE OF NAVAL RESEARCH

Grant or Contract N00014-87-K-0131

R & T Code 4132016

Technical Report No. 5

Monolayer Formation Characteristics of Novel Organic Molecules with
Nonlinear Optically Active Moieties

S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and
S.K. Tripathy

Prepared for publication in

Thin Solid Films, Proceedings of the Fourth International Conference
On Langmuir-Blodgett Films, April 24-29, 1989, Tsukuba, Japan.

University of Lowell
Polymer Science Program
Lowell, Massachusetts 01854

May 31, 1989

Reproduction in whole, or in part, is permitted for any purpose of the United
States Government.

This document has been approved for public release and sale: its distribution
is unlimited.

DTIC
ELECTE
JUL 25 1989
S B D

89 7 25 052

REPORT DOCUMENTATION PAGE

| | | | |
|--|--|---|-------------------------|
| 1a. REPORT SECURITY CLASSIFICATION | | 1b. RESTRICTIVE MARKINGS | |
| 2a. SECURITY CLASSIFICATION AUTHORITY | | 3. DISTRIBUTION/AVAILABILITY OF REPORT | |
| 2b. DECLASSIFICATION/DOWNGRADING SCHEDULE | | For unlimited distribution and release. | |
| 4. PERFORMING ORGANIZATION REPORT NUMBER(S) | | 5. MONITORING ORGANIZATION REPORT NUMBER(S) | |
| 6a. NAME OF PERFORMING ORGANIZATION University of Lowell | 6b. OFFICE SYMBOL (If applicable) | 7a. NAME OF MONITORING ORGANIZATION | |
| 6c. ADDRESS (City, State, and ZIP Code) University Avenue Lowell, MA 01854 | | 7b. ADDRESS (City, State, and ZIP Code) | |
| 8a. NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research | 8b. OFFICE SYMBOL (If applicable) | 9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-87-K-0131 | |
| 8c. ADDRESS (City, State, and ZIP Code) Chemistry Division Arlington, VA 22217 | | 10. SOURCE OF FUNDING NUMBERS | |
| | | PROGRAM ELEMENT NO. | PROJECT NO. |
| | | TASK NO. | WORK UNIT ACCESSION NO. |
| 11. TITLE (Include Security Classification) Monolayer Formation Characteristics of Novel Organic Molecules with Nonlinear Optically Active Moieties | | | |
| 12. PERSONAL AUTHOR(S) S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K. Tripathy | | | |
| 13a. TYPE OF REPORT (5) technical | 13b. TIME COVERED FROM 7/88 TO 7/89 | 14. DATE OF REPORT (Year, Month, Day) 89-5-29 | 15. PAGE COUNT (14) |
| 16. SUPPLEMENTARY NOTATION to be published in Thin Solid Films, Proceedings of the Fourth International Conference On Langmuir-Blodgett Films, April 24-29, 1989, Tsukuba, Japan | | | |
| 17. COSATI CODES | | 18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) | |
| FIELD | GROUP | SUB-GROUP | |
| | | | |
| 19. ABSTRACT (Continue on reverse, if necessary and identify by block number) A number of novel electroactive materials with amphiphilic molecular structure containing COOH, OH, NMe ₂ , OMe, NO ₂ and CN were synthesized. This paper discusses the monolayer forming ability of these novel compounds. The stability of the monolayer as a function of pH, temperature, composition of the material in mixed monolayers and the nature of the subphase are investigated. Appropriate choice of experimental conditions under which a stable monolayer is obtained for each material is indicated. (AW) ← | | | |
| 20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS | | 21. ABSTRACT SECURITY CLASSIFICATION | |
| 22a. NAME OF RESPONSIBLE INDIVIDUAL | | 22b. TELEPHONE (Include Area Code) | 22c. OFFICE SYMBOL |

A - MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES

S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and
S.K. Tripathy

Departments of Chemistry and Physics-Polymer Program
University of Lowell
Lowell, Massachusetts 01854, U.S.A.

INTRODUCTION

Organic materials have recently been recognized as promising candidates for nonlinear optics (NLO) applications in view of their fast response time and large non-resonant nonlinear effects in comparison with their inorganic counterparts¹⁻³. Novel organic materials that form molecular crystals and polymers with optimized molecular structure are therefore being synthesized and their NLO response assessed in attempts to obtain superior material performance. Another advantage of organic and polymeric materials is their relative ease of processing. It is possible to fabricate ultra thin films of organic NLO material that are suitably designed using the Langmuir-Blodgett (L-B) technique.

Using L-B technique it is possible to construct mono- and multilayers of organic compounds on a suitable substrate⁴. In so doing, precise control of the molecular organization and thickness (at nanometer levels) can be achieved. Optical properties of thin films, such as reflectance and transmittance depend, both on the thickness and complex index of refraction of a material. Both these parameters can typically be controlled in the L-B process. Possible applications of this technique are adequately covered in several reviews and special issues^{5,6}.

We recently reported⁷ the design and synthesis of a class of organic compounds (Schiff base) possessing a large second order molecular hyperpolarizability, β . By attaching these quadratic NLO active groups to the

conjugated polymeric backbone such as polydiacetylenes (PDA's) we expect to obtain a unique material which is NLO active at both quadratic and cubic levels. PDA's have already been shown to possess one of the largest known non resonant cubic NLO susceptibility (χ^3) values^{8,9}. We have synthesized a number of liquid crystalline quadratic NLO active compounds and their diacetylene derivatives. We report here a systematic study (using the L-B technique) on the monolayer forming ability of these novel compounds. In cases where they do form well defined monolayers, the stability of the monolayer obtained under different experimental conditions are investigated.

EXPERIMENTAL

The candidate materials used in this investigation were synthesized as per the scheme shown in Fig. 1a. Details of the synthetic procedures used will be published elsewhere¹⁰. The monolayer studies were carried out using a commercial Lauda film balance. To form monolayers, compounds dissolved in chloroform (1-2 mM concentration) were spread onto water at the desired pH or 10^{-4} M CdCl_2 solution as the subphase. A Millipore Milli-Q purification system was used for subphase preparation and a Lauda constant temperature bath was used to control the subphase temperature.

RESULTS AND DISCUSSION

The molecular structures of the candidate materials are shown in Fig. 1b. The molecular structures of the NLO active Schiff base compounds are indicated by M1, M2, M5 and M6. The surfactive compounds used in this study containing these functionalities are indicated by the roman numerals, I-VIII. Step 1 in Fig. 1a shows the synthetic route to the Schiff base compounds M1-M6. Steps 2 and 3 define the approach to the synthesis of the diacetylene compounds containing quadratic NLO groups. Step 4 is an intermediate stage for the synthesis of liquid crystalline compounds. I and II are intermediate compounds in our approach to

synthesize comb-like liquid crystalline polymers. The two materials contain M2 and M5 respectively as quadratic NLO active moieties which also function as mesogens. It is interesting to note that these materials themselves have been found to exhibit mesomorphic transitions and possess amphiphilic character as well, making them suitable for L-B monolayer formation. Compounds III and IV possess several interesting features: M2 and M5 as quadratic NLO active moieties; the diacetylene functionality for imparting cubic NLO activity through topochemical polymerization to a polydiacetylene; and amphiphilic character (carboxylic acid group).

The conventional approaches to render an organic compound nonlinear are to introduce strong electron donor and acceptor functionalities in its molecular structure: the NLO active moieties M1, M2, M5 and M6 possess this structural feature. We have introduced NO₂, CN, NMe₂ and OMe groups at one end of the molecule for this purpose. These groups are sufficiently polar to render them hydrophilic as well. In this sense, compounds I-IV contain surfactive groups at both ends of the molecule which introduce complications with respect to their alignment at the air-water interface. In order to understand the surfactive nature of these functionalities and to possibly resolve this "ambi-surfactive" character of molecules I-IV (through an appropriate choice of experimental conditions), compounds V-VIII were synthesized and subjected to L-B monolayer studies. The principal objective of this systematic study is to explore the conditions under which a stable L-B monolayer can be obtained for each molecule shown in Fig. 1. Results are summarized in Table I in which the appropriate combination of experimental conditions for obtaining a stable monolayer for each material is indicated.

Effect of subphase temperature: Isotherms were collected for all the materials shown in Table I as a function of temperature at the chosen pH. For



| | |
|-------|----------------------|
| Codes | |
| Dist | Avail and/or Special |
| A-1 | |

these materials we find that increasing temperature has a destabilizing effect on the monolayer stability (Fig. 2a). In general, the whole compression isotherm is shifted toward lower values of area/molecule on increasing the temperature (Fig. 2b). The upper limit on temperature in this study was 30° C because in many cases no monolayer was formed at or above this temperature. Many of our compounds exhibit interesting phase transformations during the course of monolayer formation. Significant shifts in these phase transitions are observed on changing the subphase temperature. This is illustrated in Fig. 2b for compound I. Phase transitions exhibited by this molecule probably indicate the different conformational arrangements adopted by the molecule at the air-water interface. Lowering the temperature has a stabilizing effect not only on the monolayer formed, but also on the intermediate phases during the process of monolayer formation. This in turn would lengthen the plateau region. This can be seen in Fig. 2b, where the plateau length gradually increases as the temperature is decreased.

Effect of subphase pH: Subphase pH has a remarkable effect on the nature of the monolayer formed. Owing to differences in the polarity of the hydrophilic head group across the spectrum of molecules (see Table I) used in this investigation, anchoring of these groups at the water surface can be influenced by changing the subphase pH. Desired pH was obtained by adding 1M solutions of either NaOH or HCl to the subphase. The effect of subphase pH on the compression isotherms for compounds V-VIII is quite dramatic and in fact, a monolayer did not form at all at neutral pH. The typical effect of subphase pH on the compression isotherm is illustrated for a representative compound VIII in Fig. 3. The actual pH range at which a reasonable monolayer is formed depends on the nature of the polar head group. In the case of compounds III and IV, however, subphase pH does not significantly change the monolayer formed.

This may be due to strong anchoring (on water) of highly hydrophilic COOH head group present in these compounds.

Miscellaneous effects: We have formed mixed monolayers of a few representative materials with classical monolayer forming compounds such as stearic acid and nonacosanoic acid. Typical isotherms obtained are represented in Figs. 4a and 4b, respectively. Our intention in this case is to determine the composition of the mixture for which a reasonable mixed monolayer can be obtained for the material under investigation. Compounds I and III by themselves exhibit low collapse pressure (see Fig. 2b) and large fluctuations in pressure during transfer on to solid substrates. In the mixed state however we see higher collapse pressures (Fig. 4a, 4b) and better monolayer stability during transfer.

For compounds III, IV and IX (containing carboxylic acid functionality as the hydrophilic head group) we find that using 0.1 mM solutions of CoCl_2 or CdCl_2 increased the stability of the monolayer formed.

CONCLUSION

We have synthesized several novel organic compounds in which structural units possessing large second and third order NLO response have been assembled together. Amphiphilic structural moieties have also been built in to these molecules to facilitate thin film processing by the L-B technique. Through a systematic study, we have identified the appropriate choice of experimental conditions (see Table I) to obtain a stable L-B monolayer for different classes of nonlinear optical materials possessing hydrophilic head groups of varying polarity. The linear and non-linear optical properties will be reported elsewhere.

ACKNOWLEDGEMENTS

This work was supported in part by the Office of Naval Research.

REFERENCES

- 1 D.S. Chemla and J. Zyss, eds., NLO Properties of Organic Molecules and crystals, Academic Press, Inc., New York, 1987.
- 2 D.J. Williams, ed., NLO Properties of Organic and Polymeric Materials, ACS Symp. Ser. 233, ACS, Washington, D.C., 1983.
- 3 P.N. Prasad and D.R. Ulrich, Nonlinear Optical and Electroactive Polymers, Plenum, New York, 1987.
- 4 G.L. Gaines, Insoluble Monolayers at Liquid-Gas Interfaces, Wiley, New York, 1966.
- 5 J.D. Swalen, J. Mol. Elec., Vol. 2, (1986) 155.
- 6 G.G. Roberts, Contemp. Phys. Vol. 25, No. 2, (1984) 109.
- 7 R.S. Kumar, J. Kumar, S.S. Kumar and A. Blumstein and S.K. Tripathy, MACRO 88 Proceedings, IUPAC Macromolecules, Kyoto, Japan, 1988, to be published.
- 8 G.M. Carter, Y.J. Chen and S.K. Tripathy in NLO Properties of Organic and Polymeric Materials, D.J. Williams, ed., ACS Symp. Ser. 233, ACS, Washington, D.C., 1983 p. 213.
- 9 G.M. Carter, Y.J. Chen, M.F. Rubner, D.J. Sandman, M.K. Thakur and S.K. Tripathy in ref. 1.
- 10 Organic Materials for Efficient Nonlinear Optics II. Synthesis and Characterization of Diacetylene Derivatives Containing NLO Active Moieties, To be submitted to Macromolecules.

TABLE I. CONDITIONS FOR THE FORMATION OF STABLE MONOLAYER

| COMPOUND NUMBER ^a | SURFACTIVE GROUP | CHOICE OF EXPERIMENTAL CONDITIONS | | | AREAMOLECULE | |
|---------------------------------|-----------------------|-----------------------------------|---------------------|-------------------------------------|-------------------------------------|------------------------|
| | | PH | TEMPERATURE (°C) | SUBPHASE | CALCULATED (Å ² /MOL) | ESTIMATED ^b |
| I | OH, NO ₂ | 7 | 10.3 | water | 32.4 | 30.3 |
| | | 10 | 20 | water | 32.7 | |
| III | COOH, NO ₂ | 7 | 10.3 | water | 24.1 | 23.5 |
| IV | COOH, CN | - | 12.5 | CdCl ₂ .H ₂ O | 32.04 | 33.6 |
| V | NMe ₂ | 3.8 | 12.5, 20 | water | 24.8 | 31.4 |
| VII | CN | 8.1 | 12.5, 20 | water | 29.2 | 30.3 |
| VIII | OMe | 7 | 12.5 | water | 40 | 36.6 |
| | | 8.1 | 12.5, 20 | water | 38.6 | |

^acompounds II, VI did not form satisfactory monolayers.

^bestimated area of the molecule in its completely extended conformation.

FIG. 1a. SYNTHETIC SCHEME FOR THE PREPARATION OF THE
COMPOUNDS INVESTIGATED.

MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC
MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES

S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K.
Tripathy





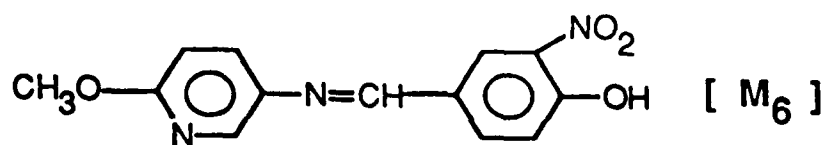
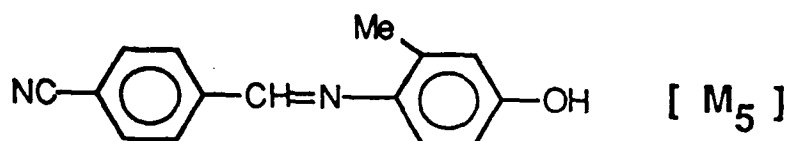
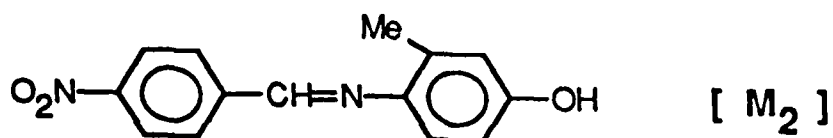
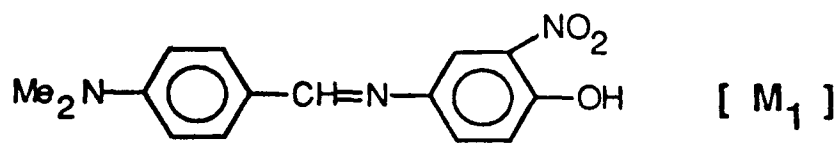


FIG 1b

**FIG. 1b. MOLECULAR STRUCTURES OF THE COMPOUNDS INVESTIGATED;
ROMAN NUMERALS REFER TO COMPOUND NUMBERS USED IN THE TEXT.**

**MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC
MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES**

**S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K.
Tripathy**

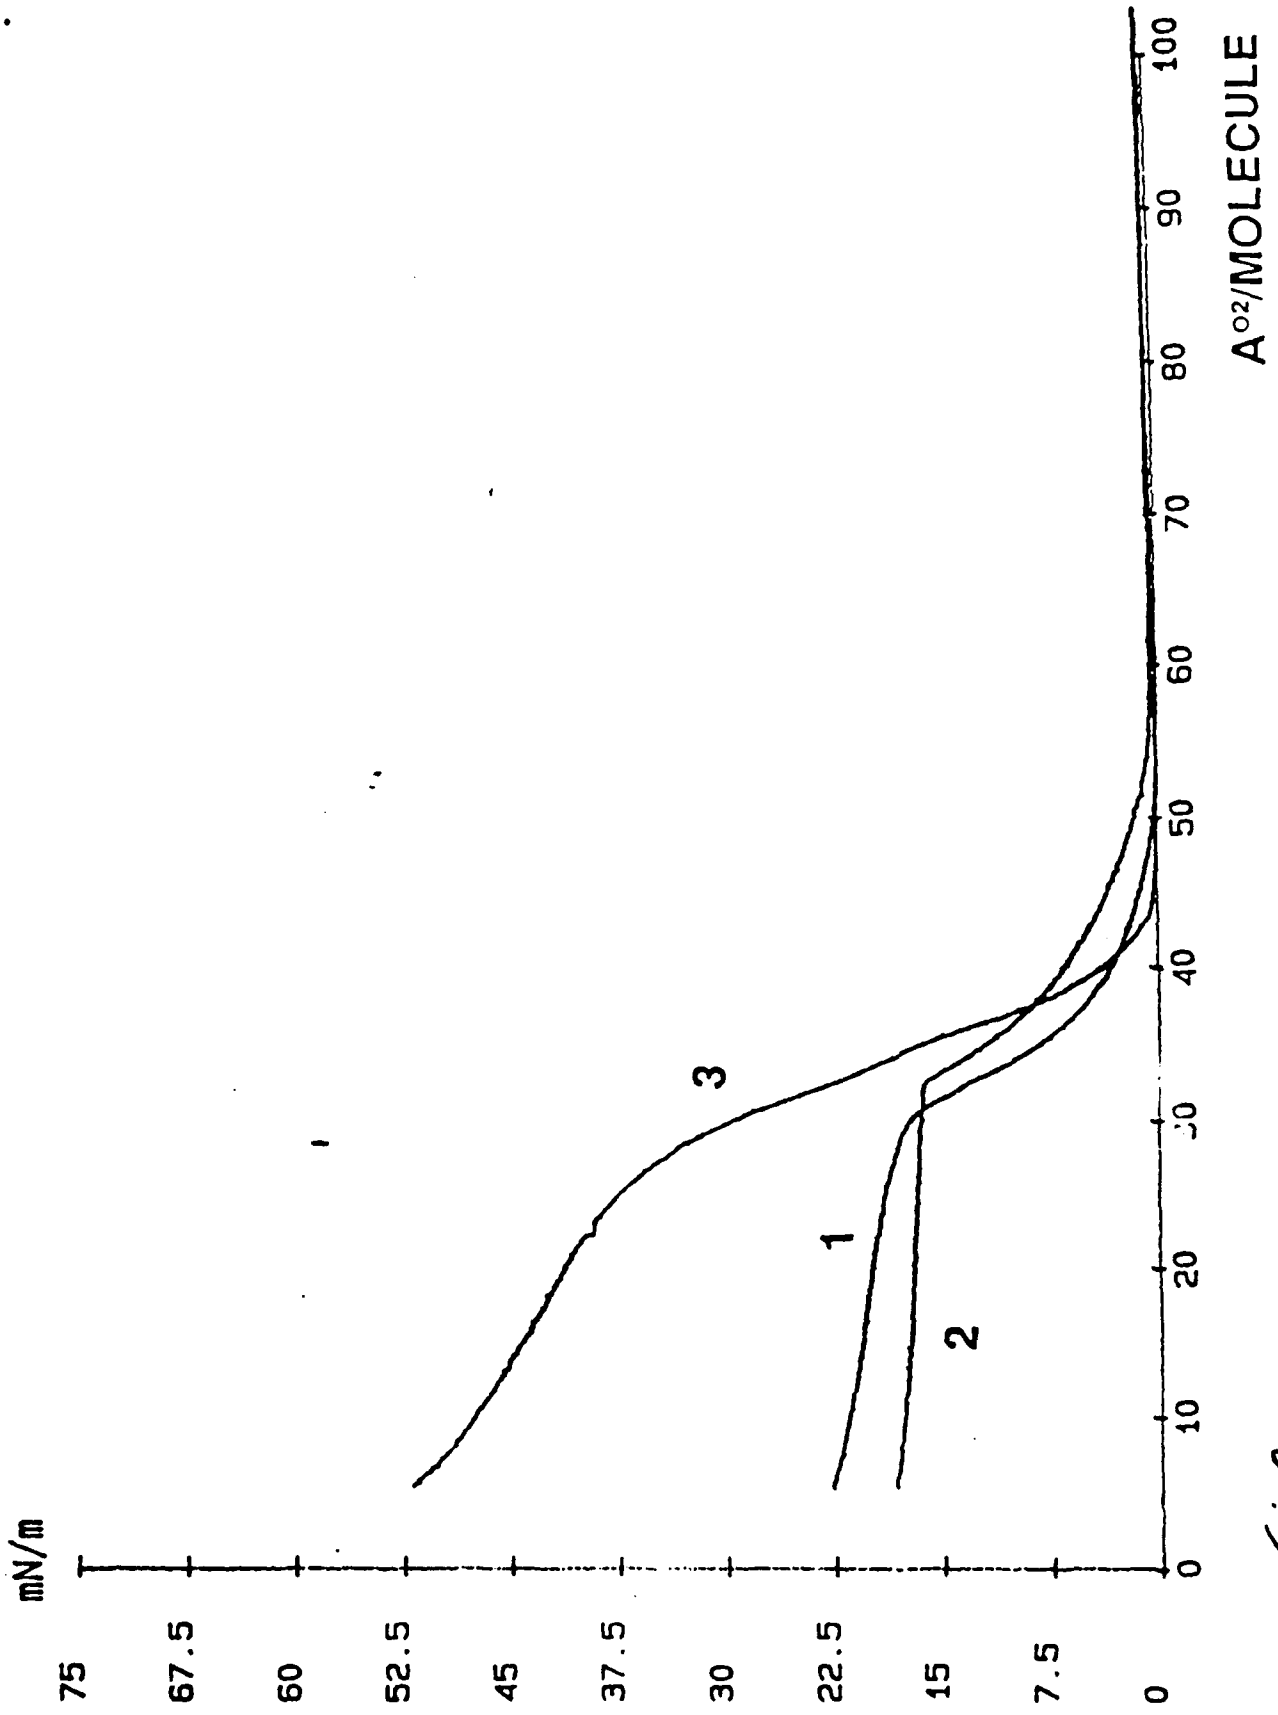


Fig. 2a

h.

FIG. 2a. EFFECT OF TEMPERATURE ON THE MONOLAYER FORMATION OF
COMPOUND VIII. 1: T=20°C; 2: T=30°C; 3: T=12.5°C

MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC
MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES

S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K.
Tripathy

FIG. 2b. EFFECT OF TEMPERATURE ON THE MONOLAYER FORMATION OF
COMPOUND I. 1: T=10°C; 2: T=15°C; 3: T=20°C; 4: T=25°C

MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC
MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES
S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K.
Tripathy

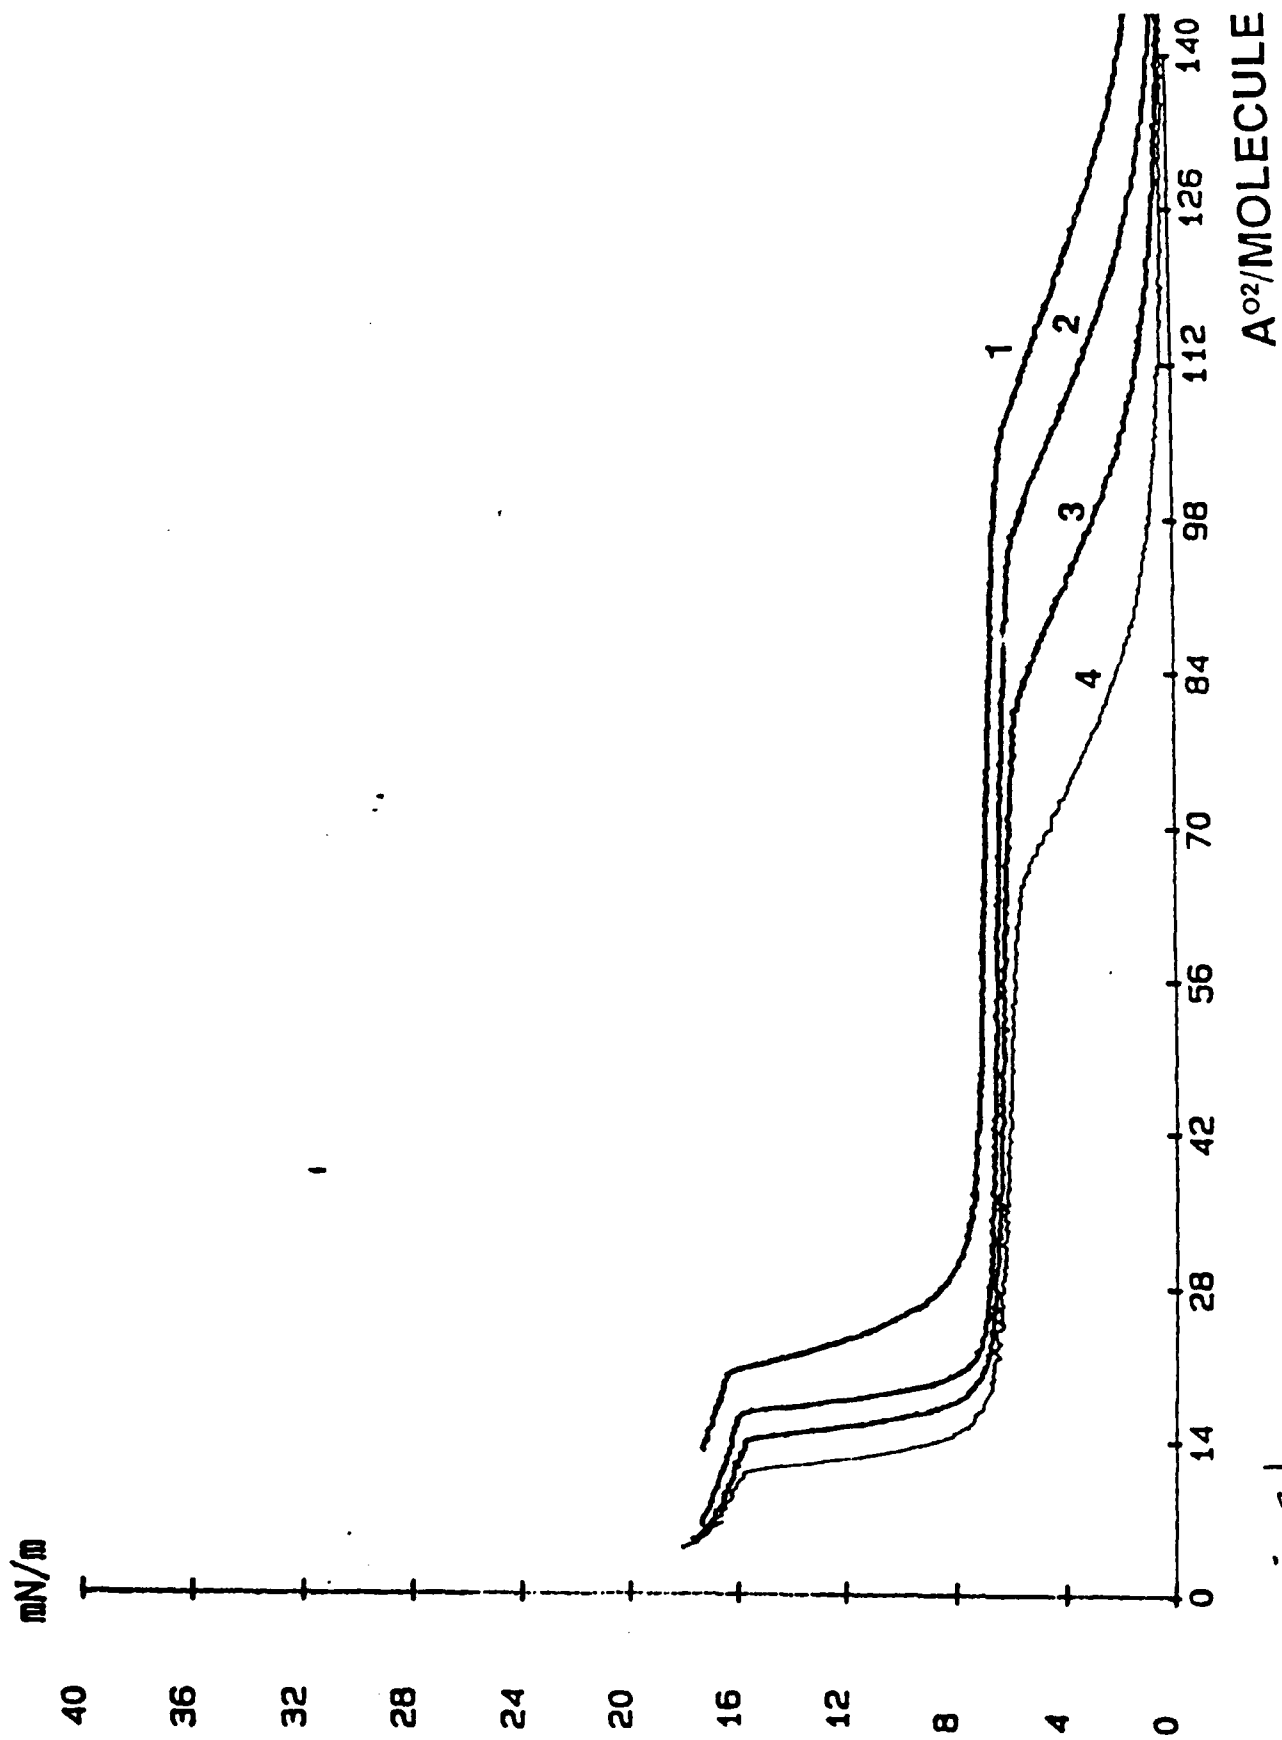


Fig 7.b

FIG. 3. EFFECT OF SUBPHASE pH ON THE MONOLAYER FORMATION OF
COMPOUND VIII. 1: pH 8.1; 2: pH 7; 3: pH 3.8

MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC
MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES

S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K.
Tripathy

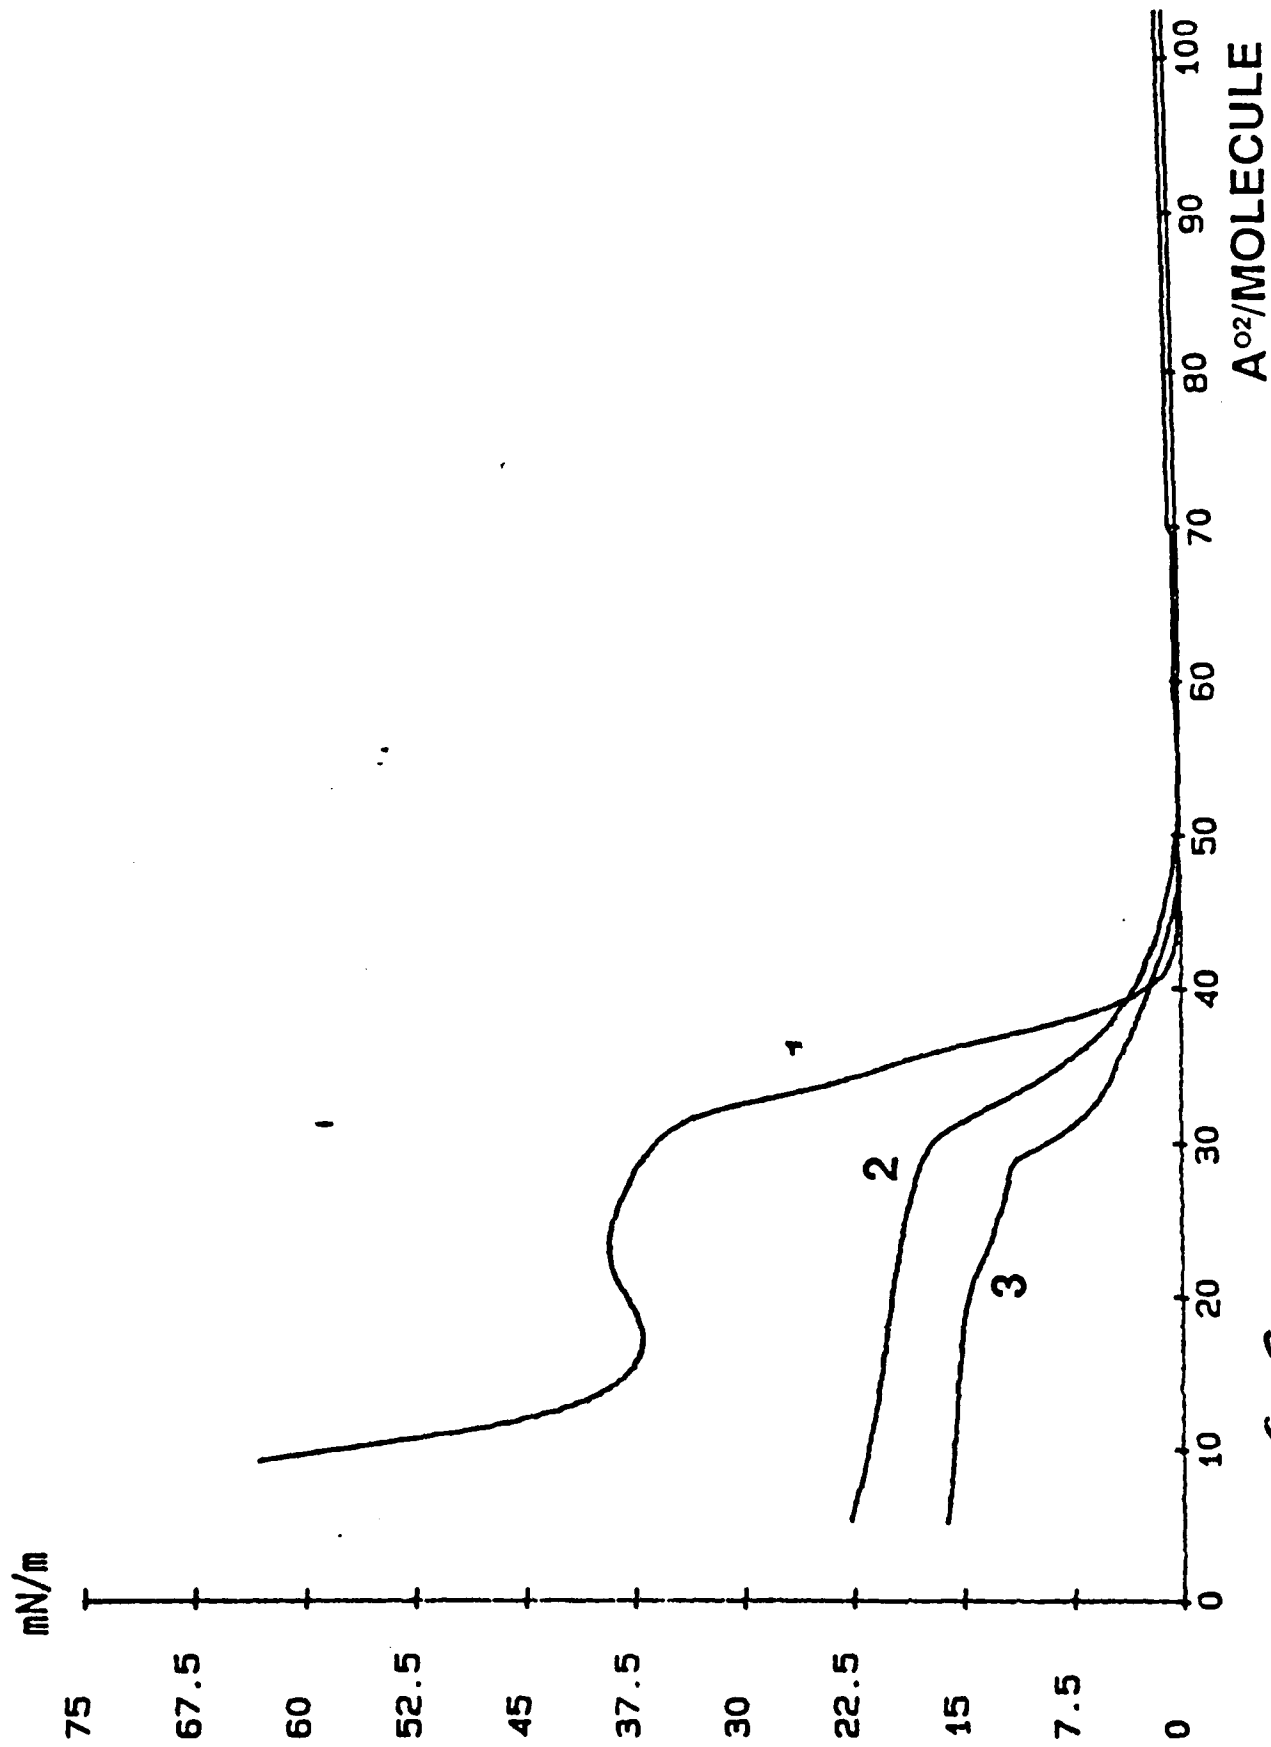


Fig. 3

FIG. 4a. MIXED MONOLAYER OF COMPOUND I WITH STEARIC ACID.

MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC
MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES

S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K.
Tripathy

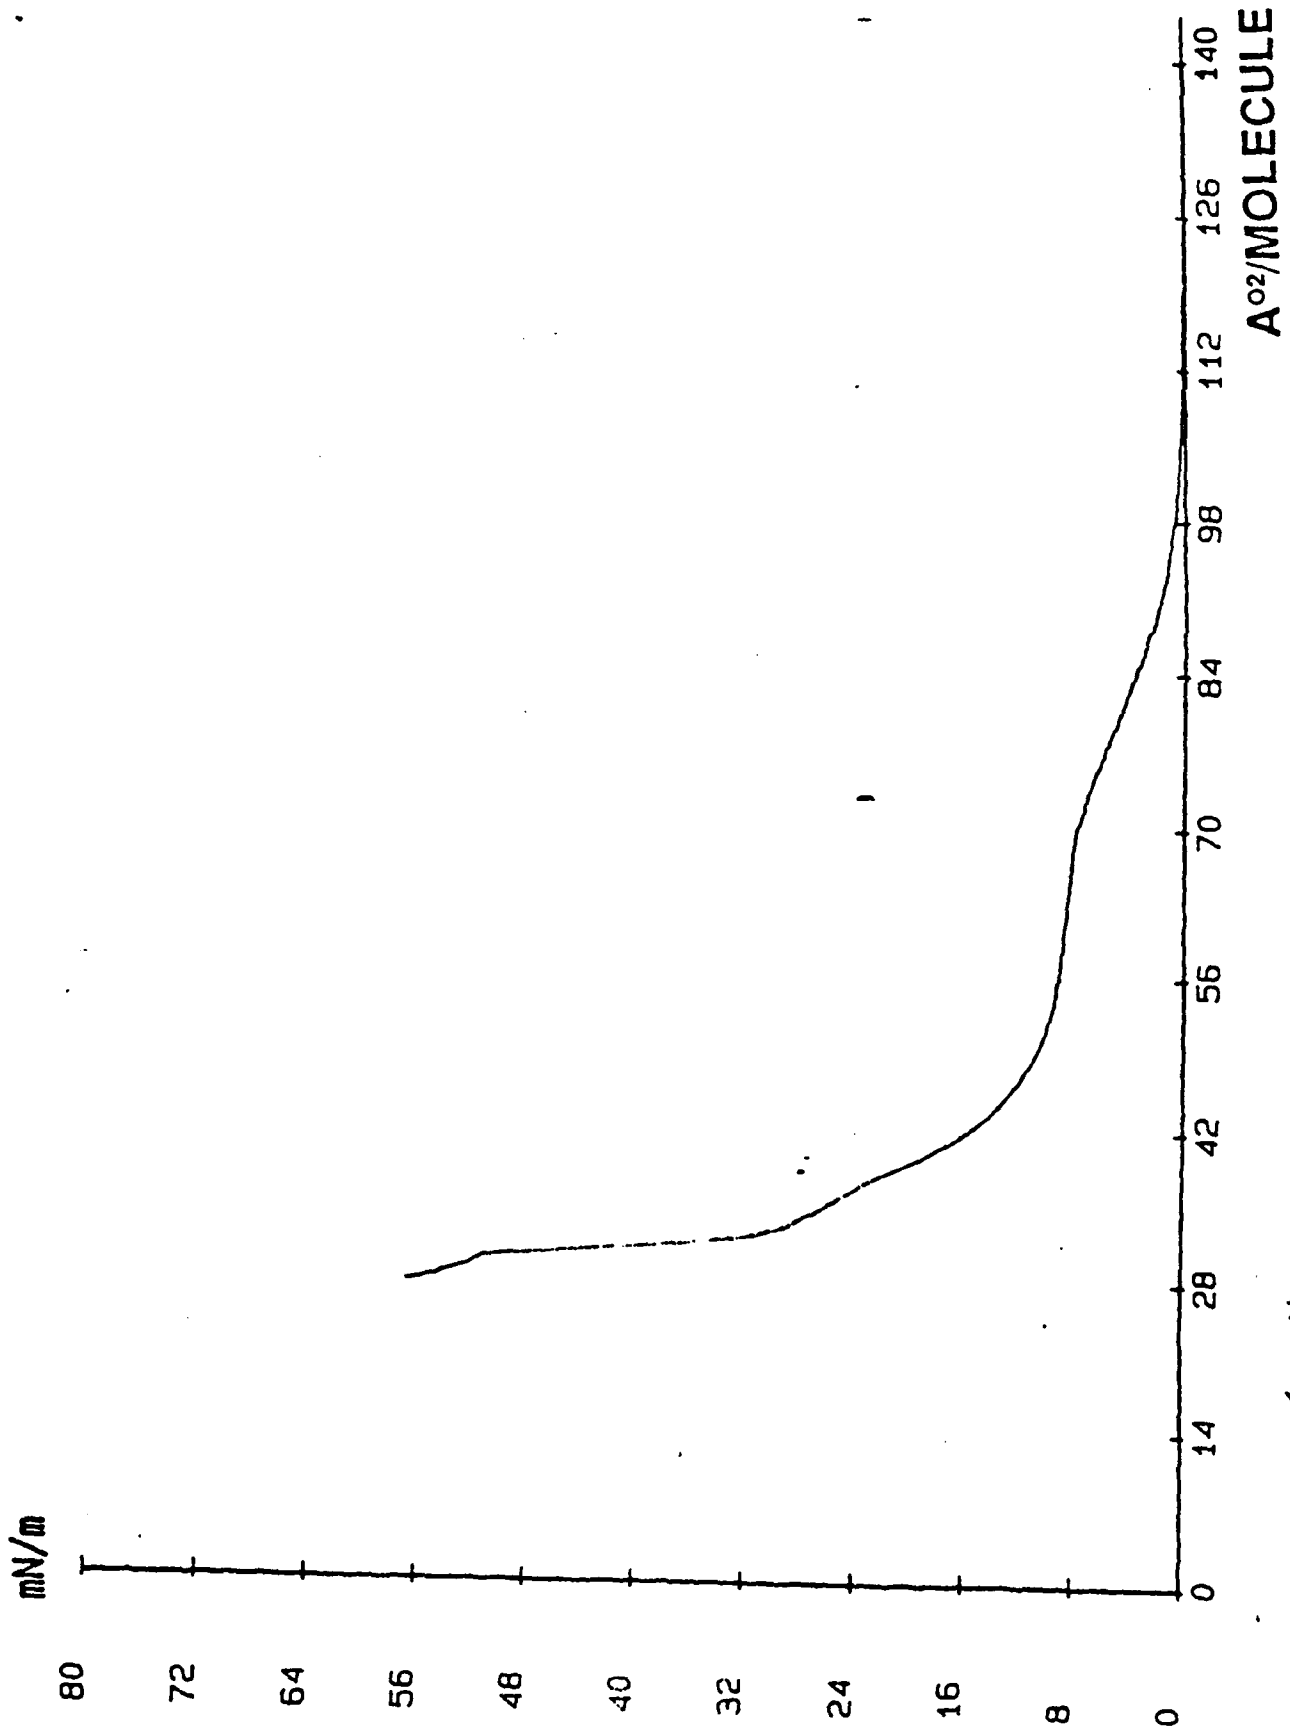


Fig. 4a

FIG. 4b. MIXED MONOLAYER OF COMPOUND III WITH 10.12
NONACOSADIYNOIC ACID.

MONOLAYER FORMATION CHARACTERISTICS OF NOVEL ORGANIC
MOLECULES WITH NONLINEAR OPTICALLY ACTIVE MOIETIES

S.S. Kumar, R.S. Kumar, L.A. Samuelson, J. Kumar, A. Blumstein and S.K.
Tripathy

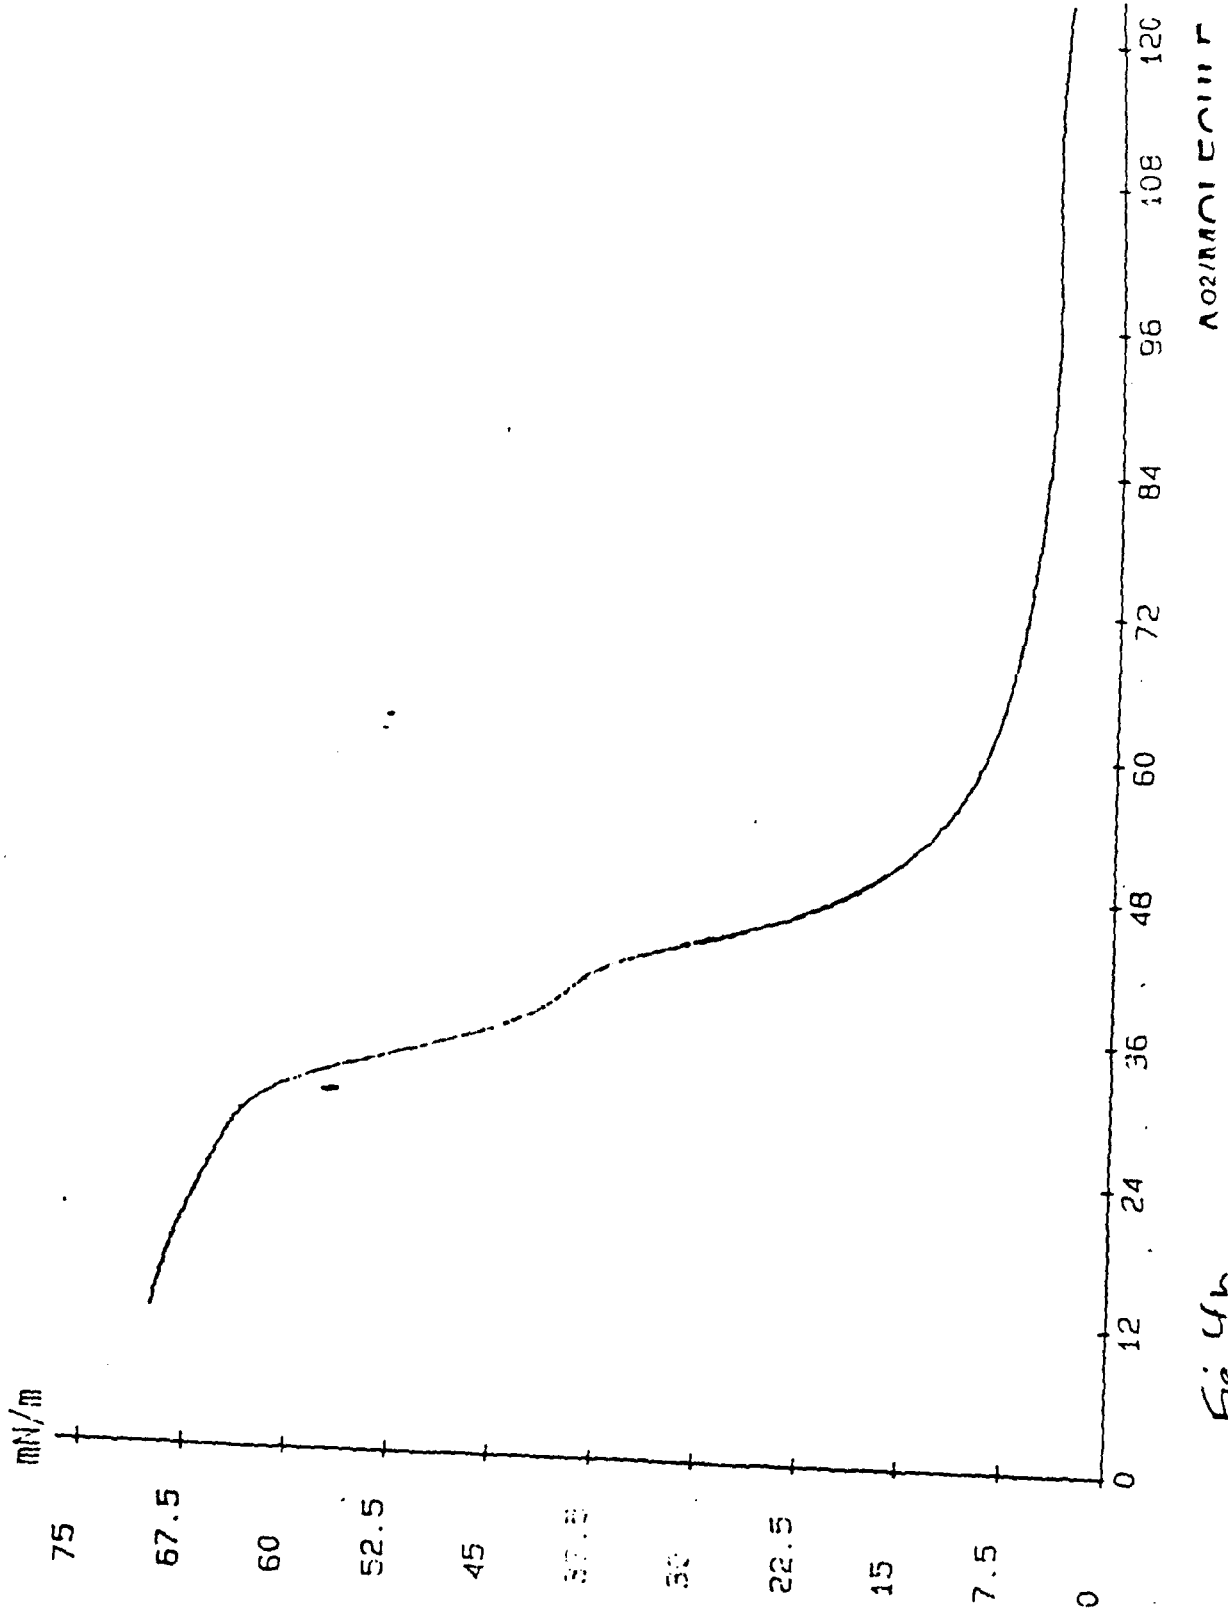


Fig 4h

h.c.

TECHNICAL REPORT DISTRIBUTION LIST, GENERAL

| | <u>No. Copies</u> | | <u>No. Copies</u> |
|--|------------------------------|--|-----------------------|
| Office of Naval Research Chemistry Division, Code 1113 800 North Quincy Street Arlington, VA 22217-5000 | 3 | Dr. Ronald L. Atkins Chemistry Division (Code 385) Naval Weapons Center China Lake, CA 93555-6001 | 1 |
| Commanding Officer Naval Weapons Support Center Attn: Dr. Bernard E. Doua Crane, IN 47522-5050 | 1 | Chief of Naval Research Special Assistant for Marine Corps Matters Code OOMC 800 North Quincy Street Arlington, VA 22217-5000 | 1 |
| Dr. Richard W. Drisko Naval Civil Engineering Laboratory Code L52 Port Hueneme, California 93043 | 1 | Dr. Bernadette Eichinger Naval Ship Systems Engineering Station Code 053 Philadelphia Naval Base Philadelphia, PA 19112 | 1 |
| Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314 | 2 <u>high quality</u> | Dr. Sachio Yamamoto Naval Ocean Systems Center Code 52 San Diego, CA 92152-5000 | 1 |
| David Taylor Research Center Dr. Eugene C. Fischer Annapolis, MD 21402-5067 | 1 | David Taylor Research Center Dr. Harold H. Singerman Annapolis, MD 21402-5067 ATTN: Code 283 | 1 |
| Dr. James S. Murday Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000 | 1 | | |