

ARL-STRUC-TM-513

AR-005-619

4



DEPARTMENT OF DEFENCE
DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION
AERONAUTICAL RESEARCH LABORATORY
MELBOURNE, VICTORIA

Aircraft Structures Technical Memorandum 513

**A SUMMARY OF THE BODNER-STOUFFER
CONSTITUTIVE MODEL (U)**

by

N. BRIDGFORD

DTIC
ELECTE
NOV. 24 1989
S B D
CB

Approved for Public Release

(C) COMMONWEALTH OF AUSTRALIA 1989

MAY 1989

89 11 21 046

AD-A214 532

AR-005-619

DEPARTMENT OF DEFENCE
DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION
AERONAUTICAL RESEARCH LABORATORY

Aircraft Structures Technical Memorandum 513

**A SUMMARY OF THE BODNER-STOUFFER
CONSTITUTIVE MODEL (U)**

by

N. BRIDGFORD

SUMMARY

A set of constitutive equations has recently been developed to model non-linear material behaviour of high temperature superalloys. This paper summarises the governing equations of this new model and presents a simple FORTRAN program which implements these equations for the one-dimensional case.



(C) COMMONWEALTH OF AUSTRALIA 1989

POSTAL ADDRESS: Director, Aeronautical Research Laboratory,
P.O. Box 4331, Melbourne, Victoria, 3001, Australia

CONTENTS

1. INTRODUCTION 1

2. NEW UNIFIED CONSTITUTIVE MODEL 1

 2.1 Theory 1

 2.2 Program Summary 4

 2.3 Detailed Description 4

3. DISCUSSION 8

REFERENCES

FIGURES

APPENDIX

DISTRIBUTION LIST

DOCUMENT CONTROL DATA

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

1. INTRODUCTION

Classical techniques of modelling creep and plasticity have a high degree of accuracy provided the inelastic strains are kept small. However, they are poor in describing material behaviour where significant inelastic strains or unloading are involved.

In a recent investigation [1], a number of "unified" constitutive models were examined. In these approaches, a single inelastic strain tensor is used to model both creep and plasticity. A new constitutive equation was then proposed.

This report describes this new approach, and discusses a FORTRAN program * which uses these new equations to predict material behaviour. Given either stress or strain values as input data, it evaluates the "state variables", i.e. drag stress, back stress etc., the inelastic strain rate and the inelastic work.

2. NEW UNIFIED CONSTITUTIVE MODEL

2.1 Theory

The unified constitutive model developed by Ramaswamy [1] is based on the generic back stress and drag stress model proposed by Bodner [2] and Stouffer [3]. The Bodner-Stouffer flow law can be written as

$$\dot{\epsilon}_{ij}^I = \lambda S_{ij} \quad (1)$$

where λ is a scalar material function which can be found using a procedure suggested by Bodner and Stouffer[3]. Including a back stress in the model

* Developed by Prof. D.C. Stouffer and V.S. Battachar at the University of Cincinnati, Ohio, U.S.A.

allows the inelastic strain rate vector $\dot{\epsilon}_{ij}^I$ and the deviatoric stress vector S_{ij} to have different directions, and results in a flow rule of the form

$$\dot{\epsilon}_{ij}^I = \lambda (S_{ij} - \Omega_{ij}). \quad (2)$$

Squaring (2) and defining

$$D_2^I = \frac{1}{2} \dot{\epsilon}_{ij}^I \dot{\epsilon}_{ij}^I \quad (3)$$

and

$$K_2 = \frac{1}{2} (S_{ij} - \Omega_{ij}) (S_{ij} - \Omega_{ij}) \quad (4)$$

as the second invariants of the inelastic strain rate tensor and the effective deviatoric stress tensor respectively, then the flow equation can be rewritten as

$$\dot{\epsilon}_{ij}^I = \sqrt{D_2^I} \frac{(S_{ij} - \Omega_{ij})}{\sqrt{K_2}}. \quad (5)$$

It is normal to assume the form of $\sqrt{D_2^I}$ as

$$\sqrt{D_2^I} = D \exp \left[-\frac{A}{2} \left(\frac{Z^2}{3K_2} \right)^n \right] \quad (6)$$

where D , A and n are temperature dependent material parameters. In this case the general flow equation can be written as

$$\dot{\epsilon}_{ij}^I = D \exp \left[-\frac{A}{2} \left(\frac{Z^2}{3K_2} \right)^n \right] \frac{(S_{ij} - \Omega_{ij})}{\sqrt{K_2}}. \quad (7)$$

This is the form of the flow equation used in the FORTRAN program.

The back stress Ω and the drag stress Z used in these equations are "state variables" which cannot be measured directly. They are represented in the form of evolution equations, where their rate of change with respect to time depends upon the current state of stress, inelastic strain rate, temperature and internal variables, viz:

$$\dot{\Omega} = F_1 (\sigma_{ij}, \dot{\epsilon}_{ij}^I, \Omega_{ij}, Z, T) \quad (8)$$

and

$$\dot{Z} = F_2 (\sigma_{ij}, \dot{\epsilon}_{ij}^I, \Omega_{ij}, Z, T). \quad (9)$$

The multi-axial form of the back stress evolution equation used in the FORTRAN program is

$$\dot{\Omega}_{ij}^I = f_1 \dot{\epsilon}_{ij}^I - \frac{3}{2} f_1 \frac{\Omega_{ij}}{\Omega_{max}} \dot{\epsilon}_{eff}^I \quad (10)$$

where f_1 , G and Ω_{max} are scalar parameters determined from uniaxial experiments, and where, for a uniaxial loading condition, the effective inelastic strain rate is defined as

$$\dot{\epsilon}_{eff}^I = \sqrt{\frac{2}{3} \dot{\epsilon}_{ij}^I \dot{\epsilon}_{ij}^I}. \quad (11)$$

Also,

$$\Omega_{ij} = \frac{G}{E} S_{ij} + \Omega_{ij}^I \quad (12)$$

The drag stress Z is a scalar quantity, and is represented by the evolution equation

$$\dot{Z} = m(Z_1 - Z_0)\dot{W}^I + R_2. \quad (13)$$

If temperature effects are insignificant then eqn (13) can be integrated to give

$$Z = Z_1 + (Z_0 - Z_1) e^{-mW^I} \quad (14)$$

where Z_0 is the initial value of Z , Z_1 is the saturated value of drag stress, m determines the rate of cyclic softening, and W^I is the inelastic work. Further details of the above equations and their derivations are given in reference [1], whilst reviews of current methods for predicting material behaviour are given in references [1,4].

2.2 Program Summary

A simple FORTRAN program, which we will refer to as MODEL2, has been written to implement this system of constitutive equations, though at present it is only applicable to the one-dimensional case. It may be run in either Stress or Strain control, with either isothermal or non-isothermal conditions. The loading may be either tensile, torsional or a combination of tension or torsion. Input data consists of control variables, load history points (stress or strain), and material data. A complete listing of the input required can be found in the Appendix.

The subroutines called in this program, and a brief description of their functions, are given in Figure 1. A flow chart for the program is presented in Figure 2.

2.3 Detailed Description

- Subroutines INPUT1, INPUT2 and LOADHIST read in and initialise material constants, control parameters and initial values of stress or strain.

- Subroutine TSTEP then determines the time step Δt for the inelastic constitutive equation, using current stress or strain values, the current time step and control parameters.

The new time step Δt^* is taken as the minimum of

- (i) $(\Delta t * \Delta t_{init}) / 1E - 10$
- (ii) $(\Delta t * \Delta \sigma_{max}) / |\sigma_{max}(t^*) - \sigma_{max}(t)|$
- (iii) $(\Delta t * \Delta \varepsilon_{max}) / |\varepsilon_{max}(t^*) - \varepsilon_{max}(t)|$
- (iv) $\Delta t_{max} * \Delta t,$

where Δt is current time step, Δt_{max} and Δt_{min} are the maximum and minimum time step factors respectively, Δt_{init} is the initial time step and $t^* = t + \Delta t$.

However, if $\Delta t^* < \Delta t_{min} * \Delta t$ then $\Delta t^* = \Delta t_{min} * \Delta t$.

- Subroutine INTTIME linearly interpolates the stress/strain and temperatures with respect to time. Using subroutine INTTEMP, material constants are also interpolated with respect to time for the non-isothermal case. Subroutine DCCALCS then interpolates the material stiffness matrix $[D]$ and the material compliance matrix $[C]$.

- If the program is running under strain control, inelastic strain is estimated using the equation

$$\varepsilon_{ij}^I(t^*) = \varepsilon_{ij}^I(t) + \Delta t \dot{\varepsilon}_{ij}^I(t). \quad (15)$$

- Subroutine STREPS, running under strain control, calculates elastic strains and evaluates the stresses and total strains as follows

$$\epsilon_e(t^*) = \epsilon_{ij}(t^*) - \epsilon_{ij}^I(t^*)$$

$$\sigma_{ij}(t^*) = [D]\epsilon_e(t^*) \quad (16)$$

$$\epsilon_{ij}(t^*) = \epsilon_e(t^*) + \epsilon_{ij}^I(t^*).$$

If the program is running under stress control, STREPS calculates only the elastic strains, viz:

$$\epsilon_e(t^*) = [C]\sigma_{ij}(t^*). \quad (17)$$

and the deviatoric stresses $S_{ij}(t^*)$ are calculated in subroutine DEVSTR.

• The state variables back stress, drag stress and K_2 are evaluated next, along with the total inelastic strain and the inelastic work. These calculations are performed using subroutines DRAG, EFFRAT, BACK, K2CALC, TOTISTR and WORK.

Subroutine DRAG evaluates the drag stress using eqn(14), viz:

$$Z(t^*) = Z_1 + (Z_0 - Z_1)e^{-mW^I}.$$

Subroutine EFFRAT evaluates the effective inelastic strain rate using eqn(11), viz:

$$\dot{\epsilon}_{eff}^I = \sqrt{\frac{2}{3}\epsilon_{ij}^I(t^*)\dot{\epsilon}_{ij}^I(t^*)}.$$

Subroutine PACK evaluates the inelastic back stress rate using eqn(10), and from this finds the total back stress using eqn(12), viz:

$$\Omega_{ij}(t^*) = \Omega_{ij}^I(t^*) + \frac{G}{E} S_{ij}(t^*), \quad (12)$$

where

$$\Omega_{ij}^I(t^*) = \Omega_{ij}^I(t) + \frac{\Delta t}{2} (\dot{\Omega}_{ij}^I(t) + \dot{\Omega}_{ij}^I(t^*)) \quad (18)$$

and

$$\dot{\Omega}_{ij}^I = f_1 \dot{\epsilon}_{ij}^I - \frac{3}{2} f_1 \frac{\Omega_{ij}}{\Omega_{max}} \dot{\epsilon}_{eff}^I. \quad (10)$$

Subroutine K2CALC evaluates K_2 , the second invariant of the effective deviatoric stress, from eqn(4), viz:

$$K_2 = \frac{1}{2} (S_{ij}(t^*) - \Omega_{ij}(t^*)) (S_{ij}(t^*) - \Omega_{ij}(t^*)).$$

Subroutine FLOW evaluates the inelastic strain rate using eqn(7), viz:

$$\dot{\epsilon}_{ij}^I(t^*) = D \exp \left[-\frac{A}{2} \left(\frac{Z^2}{3K_2} \right)^n \right] \frac{(S_{ij}(t^*) - \Omega_{ij}(t^*))}{\sqrt{K_2}}.$$

The total inelastic strain is found in subroutine TOTISTR

$$\epsilon_{ij}^I(t^*) = \epsilon_{ij}^I(t) + \frac{\Delta t}{2} (\dot{\epsilon}_{ij}^I(t) + \dot{\epsilon}_{ij}^I(t^*))$$

and the inelastic work is then evaluated in subroutine WORK

$$W^I(t^*) = W^I(t) + (S_{ij}(t^*) + S_{ij}(t)) (\epsilon_{ij}^I(t^*) - \epsilon_{ij}^I(t)).$$

• Subroutine CONCHK checks the convergence of inelastic strain and stress. Convergence is taken to be achieved if either

$$\varepsilon_{ij}^f(t^*) = 0$$

or

$$\sigma_{ij}(t^*) = 0$$

or if the calculated percentage error is less than the allowable percentage error for either stress or strain.

If convergence is not achieved the values are reset in subroutine RESET1, and the iteration loop re-entered as shown in the flow chart, Figure 2.

If convergence is achieved, the total strain is then determined and the appropriate values output in subroutine PRINT. Parameters such as the state variables are output to the file OUTPUT.DAT, and the values of the stresses and strains are output to the plot files PLOT1.DAT and PLOT2.DAT. If the analysis is not yet complete, a new time step Δt is determined and the solution is recalculated.

3. DISCUSSION

The program outlined in this report predicts non-linear material behaviour in the simple one-dimensional case. Predictions using this model have been shown [1,2,3] to be in good agreement with experimental results. The governing equations of the Bodner-Stouffer model summarised in this report are applicable to the three-dimensional case. This program could be extended to handle multiaxial loading conditions, and could also be incorporated into a general purpose finite element code.

REFERENCES

1. Ramaswamy, V.G., 'A Constitutive Model for the Inelastic Multiaxial Cyclic Response of a Nickel Base Superalloy René 80', NASA Contractor Report 3998, July (1986).
2. Bodner, S.R. and Partom, Y., 'Constitutive Equations for Elastic-Viscoplastic Strain-Hardening Materials', Journal of Applied Mechanics, 385-389, June (1975).
3. Stouffer, D.C. and Bodner, S.R., 'A Relationship Between Theory and Experiment for a State Variable Constitutive Equation', American Society for Testing and Materials STP, 765, 239-250, 1982.
4. Noor, A.K. and Atluri, S.N., 'Advances and Trends in Computational Structural Mechanics', AIAA Journal, 25, 7, 977-995, 1987.

SUBROUTINES:

INPUT1	- Reads Control Data
INPUT2	- Reads Material Constants
LOADHIST	- From control data this sets up the stress/strain and temperature variation curve wrt time
INTTIME	- Interpolates stress/strain & temperature wrt time
INTTEMP	- Interpolates material constants wrt temperature
DCCALC	- Calculates D and C matrix
TSTEP	- Calculates current - new time step dt
STREPS	- Calculates stresses if strain control and elastic strains if stress control
DEVSTR	- Calculates deviatoric stresses at tdt
DRAG	- Calculates Drag stress Z at tdt
EFFRAT	- Calculates effective inelastic strain rate at tdt
BACK	- Calculates Back stress Omega at tdt
K2CALC	- Calculates value of AK2 at tdt
FLOW	- Calculates inelastic strain rate at tdt
TOTISTR	- Calculates total inelastic strain at tdt
WORK	- Calculates inelastic work at tdt
CONCHK	- Check Convergence of values
RESET1	- Resets values if there is no convergence
RESET2	- Resets values if there is convergence
ERRPRT	- Prints error messages into a file
PRINT	- Prints output into a file

Figure 1: Subroutines called in MODEL2

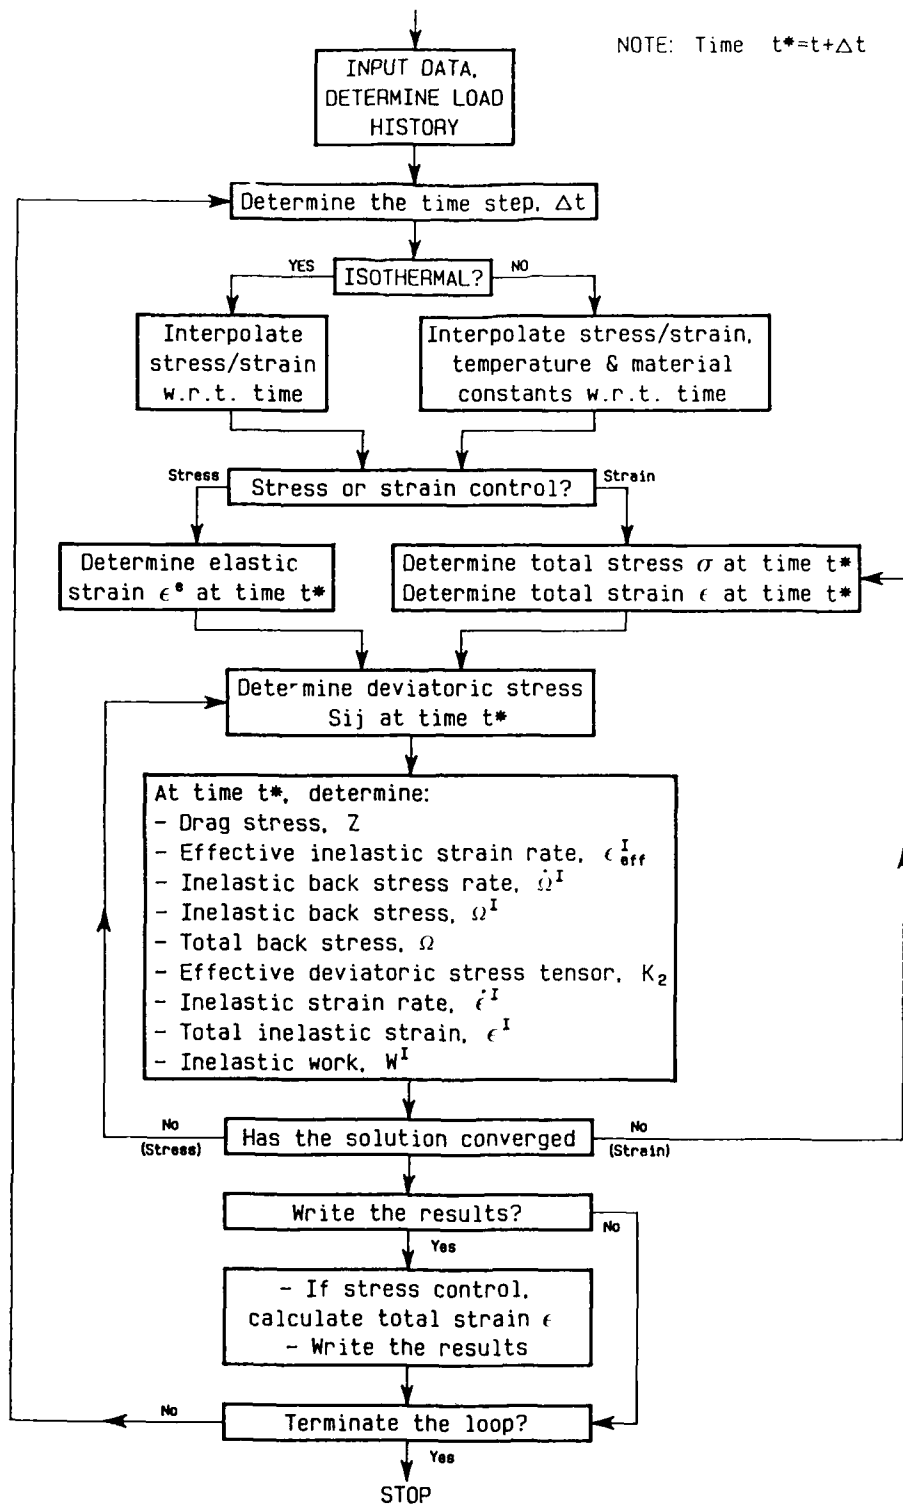


FIGURE 2. FLOW CHART FOR PROGRAM MODEL 2.F

APPENDIX: Variables used in the program MODEL2:

INPUT VARIABLES:

1. TITLES:

*ETITLE - title line in the file INPUT.DAT
**MTITLE - title line in the file MATL.DAT

2. CONTROL VARIABLES:

*NCTL - decides stress/strain control.
= 1 stress control
= 2 strain control
*NTYPE- decides the load type
= 1 tensile load only
= 2 torsional load only
= 3 tension + torsion
*NTHERM- decides isothermal/nonisothermal case
= 1 isothermal
= 2 nonisothermal
*NCYTEN- number of cycles in tension loading = or >1
*NCYTOR- number of cycles in torsion loading = or >1
*NCYTEM- number of cycles in temperature loading
= 1 isothermal
> or = 1 nonisothermal
*NP TEN - number of points in tension loading in
first cycle = or >1
*NP TOR - number of cycles in torsion loading in
first cycle = or >1
*NP TEM - number of cycles in temperature loading in
first cycle = or >1
LASTEN\
LASTOR > last points in respective loadings
LASTEM/
*TSTOP - time at which analysis is stopped = or >0
*ESTOP1- strain in the tension load direction at which
analysis is to be stopped = or >0
*ESTOP2- strain in the shear stress direction at which
analysis is to be stopped = or >0
*DTPR - output printed into OUTPUT.DAT once in DTPR time
steps (time controlled output)
= 0 if not time controlled
> 0 if time controlled
*DEPR1 - output printed once in DEPR1 increase in strain
in the tension direction (strain controlled output)
= 0 if not strain-in-axial-direction controlled
> 0 if strain-in-axial-direction controlled
*DEPR2 - output printed once in DEPR2 increase in strain
in the shear direction (strain controlled output)
= 0 if not strain-in-shear-direction controlled
> 0 if strain-in-shear-direction controlled

*CTR(20) -control variables
(1) -maximum stress step allowable in analysis
(2) -maximum inelastic strain step
(3) -maximum inelastic strain rate step
(4) -maximum time step factor
(5) -minimum time step factor
(6) -initial time step

CTR(1-6) values > 0

3. ERROR CONTROL DATA:

*PERSTR -allowable % error in stress calculations
*PEREPS -allowable % error in strain calculations
*MAXITER -maximum number of iterations allowable for convergence

4. MATERIAL CONSTANTS DATA:

**NUMCON -number of input material constants(= or <20)
**NUMTEM -number of temperatures at which material constants are being input(= or <10)
**CONS(20,10) -material constants.

CONS(I,J) I = 1,20 J = 1,10

I = 1 : A
2 : D
3 : YOUNGS MODULUS
4 : fl
5 : g
6 : m
7 : n
8 : poissons ratio
9 : ZO
10 : Z1
11 : OMEGA MAX.

CONINT(20) -interpolated material constants

D(6,6) -material stiffness matrix
C(6,6) -material compliance matrix

5. INPUT LOAD DATA:(strain inputs are tensor strain values)

*DXTTEN(10,2) - tensile load points in the first cycle
 — (stress/strain)
*DXTTOR(10,2) - torsion load points in the first cycle
 (stress/strain)
*DXTTEM(10,2) - temperature load points in the first cycle

DXT... (I,1) PARAMETER VALUE
DXT... (I,2) TIME VALUE

6. TEMPERATURE VARIABLES:

**TEMDAT(10) - temperatures at which material constants have been input

- NOTE:
1. ALL STRAIN INPUTS are TENSOR values except the values of the strains which are printed into PLOT1 and PLOT2.DAT files; these are engineering strain values.
 2. A `*' before the variable indicates it is an input from the file `INPUT.DAT'.
 3. A `**' before the variable indicates it is an input from the file `MATL.DAT'.

INTERNAL AND OUTPUT VARIABLES:

7. CALCULATED LOAD DATA:

DATTEN(500,2) - data points in the entire load history
DATTOR(500,2) - in the respective cycles.
DATTEM(500,2) -

DAT... (I,1) PARAMETER VALUE
DAT... (I,2) TIME VALUE

8. STRESS VARIABLES:

STR_t(6) - stress at time t
STR_tdt(6) - stress at time t+dt
PSTR(6) - stress at t+dt stored from the last iteration
DEVS_t(6) - deviatoric stress at time t
DEVS_tdt(6) - deviatoric stress at time t+dt

9. STRAIN VARIABLES: (all strains are tensor strains !)

EPS_t(6) - total strain at time t
EPS_tdt(6) - total strain at time t+dt

EPSE_t(6) - elastic strain at time t
EPSE_tdt(6) - elastic strain at time t+dt

EPSI_t(6) - inelastic strain at time t
EPSI_tdt(6) - inelastic strain at time t+dt
PEPSI_tdt(6) - inelastic strain at time t+dt stored from the last iteration

EPSID_t(6) - inelastic strain rate at time t
EPSID_tdt(6) - inelastic strain rate at time t+dt
PEPSID(6) - inelastic strain rate at time t+dt stored from the last iteration

EFIEPSD - effective inelastic strain rate at time t+dt

10.STATE VARIABLES:

Z_t -drag stress at time t
Z_tdt -drag stress at time t+dt

OM_t(6) -total back stress at time t
OM_tdt(6) -total back stress at time t+dt
POM(6) -total back stress at time t+dt from the previous
iteration

OMI_t(6) -inelastic back stress at time t
OMI_tdt(6) -inelastic back stress at time t+dt
POMI(6) -inelastic beck stress rate at time t+dt from the
previous iteration

OMID_t(6) -inelastic back stress rate at time t
OMID_tdt(6) -inelastic back stress rate at time t+dt
POMID(6) -inelastic back stress rate at time t+dt from
the previous iteration

AK2 - K2 value at time t+dt

11.TIME VARIABLES:

TIME -time for the present time step (same as t+dt)
dt -time increment (=TIME-previous time)
TPRINT-time at which output was printed last

12.WORK VARIABLES:

WRK_t -total inelastic work. at time t
WRK_tdt -total inelastic work at time t+dt
DELWRK -increment of work from time t to time t+dt

13.TEMPERATURE VARIABLES:

TEMP -temperature at time t+dt
TEM1,TEM2 -two input temperatures between which TEMP
lies (used for interpolation of matl const.)

14.OTHER VARIABLES:

ITER -number of iterations
NCODE-convergence code
=0 converged
=1 not converged
IERCOD-code passed on to error printing subroutine

DISTRIBUTION

AUSTRALIA

Department of Defence

Defence Central

Chief Defence Scientist
FAS Science Corporate Management (shared copy)
FAS Science Policy (shared copy)
Director, Departmental Publications
Counsellor, Defence Science, London (Doc Data Sheet Only)
Counsellor, Defence Science, Washington (Doc Data Sheet Only)
S.A. to Thailand MRD (Doc Data Sheet Only)
S.A. to the DRC (Kuala Lumpur) (Doc Data Sheet Only)
OIC TRS, Defence Central Library
Document Exchange Centre, DISB (18 copies)
Joint Intelligence Organisation
Librarian H Block, Victoria Barracks, Melbourne
Director General - Army Development (NSO) (4 copies)

Aeronautical Research Laboratory

Director
Library
Divisional File - Aircraft Structures
Author: N. Bridgeford
R. Jones

Materials Research Laboratory

Director/Library

Defence Science & Technology Organisation - Salisbury

Library

Navy Office

Navy Scientific Adviser (3 copies Doc Data sheet)
Director of Naval Aircraft Engineering

Army Office

Scientific Adviser - Army (Doc Data sheet only)
US Army Research, Development and Standardisation Group

Air Force Office

Air Force Scientific Adviser
Director General Aircraft Engineering - Air Force

Department of Transport & Communication

Library

Statutory and State Authorities and Industry

Hawker de Havilland Aust Pty Ltd, Victoria, Library
Hawker de Havilland Aust Pty Ltd, Bankstown, Library
BHP, Melbourne Research Laboratories

Universities and Colleges

Adelaide

Barr Smith Library

Melbourne

Engineering Library

Monash

Hargrave Library

Newcastle

Library

New England

Library

Sydney

Engineering Library

NSW

Physical Sciences Library
Library, Australian Defence Force Academy

Queensland

Library

Tasmania

Engineering Library

Western Australia

Library
Professor B.J. Stone, Head Mechanical Engineering

RMIT

Library
Mr M. Scott, Aerospace Engineering

University College of the Northern Territory

Library

SPARES (10 copies)
TOTAL (67 copies)

DOCUMENT CONTROL DATA

PAGE CLASSIFICATION
UNCLASSIFIED

PRIVACY MARKING

1a. AR NUMBER AR-005-619	1b. ESTABLISHMENT NUMBER ARL-STRUC-TM-513	2. DOCUMENT DATE MAY 1989	3. TASK NUMBER AIR 86/012
4. TITLE A SUMMARY OF THE BODNER-STOUFFER CONSTITUTIVE MODEL (U)		5. SECURITY CLASSIFICATION (PLACE APPROPRIATE CLASSIFICATION IN BOX(S) IE. SECRET (S), CONF.(C) RESTRICTED (R), UNCLASSIFIED (U)). <div style="display: flex; justify-content: space-around;"> <div style="border: 1px solid black; padding: 2px;">U</div> <div style="border: 1px solid black; padding: 2px;">U</div> <div style="border: 1px solid black; padding: 2px;">U</div> </div> DOCUMENT TITLE ABSTRACT	6. NO. PAGES 15
8. AUTHOR(S) N. BRIDGFORD		9. DOWNGRADING/DELIMITING INSTRUCTIONS Not applicable.	
10. CORPORATE AUTHOR AND ADDRESS AERONAUTICAL RESEARCH LABORATORY P.O. BOX 4331, MELBOURNE VIC 3001		11. OFFICE/POSITION RESPONSIBLE FOR: SPONSOR _____ RAAF SECURITY _____ DOWNGRADING _____ APPROVAL _____ CSTD	
12. SECONDARY DISTRIBUTION (OF THIS DOCUMENT)		Approved for Public Release.	
OVERSEAS ENQUIRIES OUTSIDE STATED LIMITATIONS SHOULD BE REFERRED THROUGH ASDIS, DEFENCE INFORMATION SERVICES BRANCH, DEPARTMENT OF DEFENCE, CAMPBELL PARK, CANBERRA, ACT 2601			
13a. THIS DOCUMENT MAY BE ANNOUNCED IN CATALOGUES AND AWARENESS SERVICES AVAILABLE TO.... No limitations.			
13b. CITATION FOR OTHER PURPOSES (IE. CASUAL ANNOUNCEMENT) MAY BE		<input checked="" type="checkbox"/> UNRESTRICTED OR	<input type="checkbox"/> AS FOR 13a.
14. DESCRIPTORS Heat resistant alloys Models Creep properties Computer Programs Plastic properties		15. DRDA SUBJECT CATEGORIES 0046E 0071L	
16. ABSTRACT A set of constitutive equations has recently been developed to model non-linear material behaviour of high temperature superalloys. This paper summarises the governing equations of this new model and presents a simple FORTRAN program which implements these equations for the one-dimensional case.			

PAGE CLASSIFICATION UNCLASSIFIED
PRIVACY MARKING

THIS PAGE IS TO BE USED TO RECORD INFORMATION WHICH IS REQUIRED BY THE ESTABLISHMENT FOR ITS OWN USE BUT WHICH WILL NOT BE ADDED TO THE DISTIS DATA UNLESS SPECIFICALLY REQUESTED.

16. ABSTRACT (CONT.)		
17. IMPRINT AERONAUTICAL RESEARCH LABORATORY, MELBOURNE		
18. DOCUMENT SERIES AND NUMBER Aircraft Structures Technical Memorandum 513	19. COST CODE 211080	20. TYPE OF REPORT AND PERIOD COVERED
21. COMPUTER PROGRAMS USED Model 2 FORTRAN program		
22. ESTABLISHMENT FILE REF.(S)		
23. ADDITIONAL INFORMATION (AS REQUIRED)		