

## DOCUMENTATION PAGE

Form Approved  
OMB No 0704-0188

AD-A222 273 TIC LECTE MAY 29 1990 D8 D		1b RESTRICTIVE MARKINGS	
2b DECLASSIFICATION DOWNGRADING SCHEDULE		3 DISTRIBUTION / AVAILABILITY STATEMENT <b>DISTRIBUTION STATEMENT A</b> Approved for public release Distribution Unlimited	
4 PERFORMING ORGANIZATION REPORT NUMBER(S)		5 MONITORING ORGANIZATION REPORT NUMBER(S)	
6a NAME OF PERFORMING ORGANIZATION Dept. of Chemistry Cornell University	6b OFFICE SYMBOL (if applicable)	7a NAME OF MONITORING ORGANIZATION Office of Naval Research	
6c ADDRESS (City, State, and ZIP Code) Dept. of Chemistry Cornell University Ithaca, NY 14853		7b ADDRESS (City, State, and ZIP Code) Chemistry Program 800 N. Quincy Street Alexandria, VA 22217	
8a NAME OF FUNDING SPONSORING ORGANIZATION Office of Naval Research	8b OFFICE SYMBOL (if applicable)	9 PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-88-K-1039	
8c ADDRESS (City, State, and ZIP Code) Chemistry Program 800 N. Quincy St. Alexandria, VA 22217		10 SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO	PROJECT NO
		TASK NO	WORK UNIT ACCESSION NO
11 TITLE (Include Security Classification) UNCLASSIFIED: Synthesis, Structure, Electric and Magnetic Properties of CaNiN			
12 PERSONAL AUTHOR(S) Ming Y. Chern and Francis J. DiSalvo			
13a TYPE OF REPORT Technical Rpt. #5	13b TIME COVERED FROM 1989 TO 1990	14 DATE OF REPORT (Year, Month, Day) 1990, April, 30	15 PAGE COUNT
16 SUPPLEMENTARY NOTATION			
17 COSATI CODES		18 SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	Solid state nitrides	
		Electrical and magnetic properties	
		Crystal structure	
19 ABSTRACT (Continue on reverse if necessary and identify by block number) We report the synthesis and physical properties of the new ternary nitride CaNiN, prepared by the reaction of Ca <sub>3</sub> N <sub>2</sub> and Ni in N <sub>2</sub> gas at 1000°C. The structure, determined by the method of x-ray powder diffraction, is tetragonal (P4 <sub>2</sub> /mmc) with a=3.5809(2)Å, c=7.0096(3)Å, and Z=2. While the structure is a simple but uncommon one, with all atoms occupying fixed special positions, it features interesting --Ni-N-Ni-N-- linear chains. Conductivity and magnetic measurements show that CaNiN is metallic and paramagnetic.			
20 DISTRIBUTION AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21 ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a NAME OF RESPONSIBLE INDIVIDUAL Dr. Mark Ross		22b TELEPHONE (Include Area Code) 202-696-4409	22c OFFICE SYMBOL

OFFICE OF NAVAL RESEARCH

Grant or Contract N00014-88-K-0139

R&T Code 4131035

Technical Report No. 5

Synthesis, Structure, Electric and Magnetic  
Properties of  $\text{CaNiN}$

by

Ming Y. Chern and Francis J. DiSalvo

For publication

in the

Journal of Solid State Chemistry

Cornell University  
Department of Chemistry  
Ithaca, NY 14853

April 30, 1990

Reproduction in whole or in part is permitted for any purpose  
of the United States Government

This document has been approved for public release  
and sale; its distribution is unlimited

# Synthesis, Structure, Electric and Magnetic Properties of CaNiN

Ming Y. Chern and F. J. DiSalvo\*

Department of Chemistry

Cornell University

Ithaca, NY 14853



Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

## Abstract

We report the synthesis and physical properties of the new ternary nitride CaNiN, prepared by the reaction of  $\text{Ca}_3\text{N}_2$  and Ni in  $\text{N}_2$  gas at 1000 °C. The structure, determined by the method of x-ray powder diffraction, is tetragonal ( $P4_2/mmc$ ) with  $a=3.5809(2)\text{\AA}$ ,  $c=7.0096(3)\text{\AA}$ , and  $Z=2$ . While the structure is a simple but uncommon one, with all atoms occupying fixed special positions, it features interesting --Ni-N-Ni-N-- linear chains. Conductivity and magnetic measurements show that CaNiN is metallic and paramagnetic.

## Introduction

There are only few known ternary nitrides containing both transition and alkaline earth metals (1-3). Our recent research in nitrides has focused on the synthesis of ternary phases containing calcium and a transition metal; at least one new ternary compound is found in each Ca-M-N system. As part of this investigation, we report here the synthesis and properties of a new compound, CaNiN.

The oxidation state of Ni(I) in CaNiN is quite unusual for a solid state compound. Formally Ni(I) exists in hexagonal  $\text{Ni}_3\text{N}$  (4,5). But the structure of  $\text{Ni}_3\text{N}$  is basically a tripled face-centered cubic nickel framework with *interstitial* nitrogen in the octahedral holes, and has extensive Ni-Ni bonding. Another similar example is  $\text{Ni}_3\text{S}_2$  (6), in which formally Ni(I) and Ni(II) occur, but short Ni-Ni distances comparable with that in metallic nickel are again indicative of metal-metal bonding (7). In CaNiN, the Ni-Ni distance is far too long to have any Ni-Ni interaction. A complete description of this unusual phase follows.

## Sample Preparation

CaNiN was prepared by heating in an alumina crucible a pressed pellet of  $\text{Ca}_3\text{N}_2$  and fine nickel powder in an  $\text{N}_2$  atmosphere at 1000 °C for two days.  $\text{N}_2$  gas (99.995%) was further purified by passing it through a column of finely divided copper powder at 150 °C and then a column of activated molecular sieves to remove traces of  $\text{O}_2$  and  $\text{H}_2\text{O}$ . Since at 1000 °C  $\text{Ca}_3\text{N}_2$  will slowly sublime, and since it is very sensitive to even minute amounts

of  $O_2$  and  $H_2O$  remaining in the  $N_2$  gas to produce  $CaO$ , we further protected the sample by sandwiching it with two boats of fine calcium nitride powder, and we also added a 10% excess  $Ca_3N_2$  to compensate for the calcium loss from sublimation and oxide formation. The approximate stoichiometry of the ternary compound was estimated in the following way. A pellet of  $Ca_3N_2$  of similar size was simultaneously heated adjacent to the ternary phase. The weight loss from sublimation of the  $Ca_3N_2$  pellet was found to be typically 7%. The amount of second phase, identified as  $CaO$ , in the Ca-Ni-N system estimated by X-ray diffraction was about 3%. The final weight of the ternary compound then indicates a composition  $CaNiN$ . The density of the sample was measured by a simple density apparatus (8).

Since nitrogen is a light element, the nitrogen stoichiometry can not be accurately determined by the weight gain or density alone. To measure the nitrogen content, a modified Dumas method (9) was used. The sample was ground to a fine powder and was heated in a furnace in a  $CO_2$  flow. Approximately at  $700^\circ C$  the sample starts to react with  $CO_2$  to produce  $CO$ ,  $N_2$ ,  $CaCO_3$ , and  $Ni$ . The reaction was complete in 5 min. at  $1000^\circ C$ . The  $CO$  was converted back to  $CO_2$  by reaction with  $I_2O_5$ . The  $N_2$  and  $CO_2$  were then passed through a concentrated  $KOH$  solution; the  $CO_2$  was absorbed and the volume of the  $N_2$  measured. The nitrogen content determined this way gives a stoichiometry  $CaNiN_{0.98 \pm 1\%}$ .

In our first synthesis reactions, we used a -400 mesh nickel powder, but several percent of unreacted nickel remained even after several regrinding and reheating cycles. This made the magnetic susceptibility measurement difficult, because small amount of ferromagnetic nickel can overwhelm the susceptibility of most materials. When submicron size nickel powder

(Aldrich, 99.8%) was used, we could not detect free nickel either by X-ray diffraction or by a magnet after the first firing. This fact indicates that the diffusion rate for the calcium or nickel in the solid is quite low at 1000 °C.

CaNiN is a black powder and decomposes after several hours exposure to moist air to produce NH<sub>3</sub>.

### Crystal Structure

X-ray intensity data were taken on a powder sample with a Scintag XDS 2000 diffractometer using copper  $K\alpha$  radiation. The copper  $K\alpha_2$  lines were stripped using the Scintag software. Data were collected over a two theta range 5-110 degrees. The sample was loaded in an aluminum holder and covered with a 0.5 mil. thick layer of mylar in a dry box to avoid air exposure. The mylar sheet was supported by two semicircular disks standing perpendicularly to the sample so that the absorption due to the mylar is uniform and small over the whole two theta range.

The diffraction peaks were sharp and the pattern was indexed on a tetragonal unit cell by trial and error ( $a=3.5809(2)\text{\AA}$ ,  $c=7.0096(3)\text{\AA}$ ). The systematic absences ( $l=2n$  for both  $hhl$  and  $00l$ ) suggest three possible tetragonal space groups:  $P4_2mc$ ,  $P4_2c$ , and  $P4_2/mmc$ . Because the X-ray pattern has the additional feature that all the strong lines correspond to the condition either  $h+k+l=2n$  or  $hk(l=2n)$ , we chose the space group of highest number,  $P4_2/mmc$  (no. 131), and located the atoms at special positions which satisfy this observation and produce reasonable bond lengths, i.e. Ca at (2e)  $0,0,1/4$ ;  $0,0,3/4$ , Ni at (2b)  $1/2,1/2,0$ ;  $1/2,1/2,1/2$ , and N at (2c)  $0,1/2,0$ ;  $1/2,0,1/2$ . The calculated intensities

obtained by the program Lazy (10) show an excellent agreement with the measured integrated intensities (see Table I). The theoretical density derived from the above structure is  $4.17\text{g/cm}^3$ , which agrees very well with the measured density of  $4.13\text{g/cm}^3$ .

The unit cell, which contains two formula units, is shown in Fig. 1 (we have shifted the origin by  $0,0,1/4$  for a clearer view.) In the structure, nickel is coordinated linearly to nitrogen to form chains of  $\text{---Ni-N-Ni-N---}$ . The chains are stacked in the way that there are layers of parallel chains, but chains in adjacent layers run in perpendicular directions. Calcium occupies the tetrahedral holes between the layers, and nitrogen is in approximately octahedral coordination with two nickel and four calcium near-neighbor atoms. The interatomic distances are summarized in Table II.

### Conductivity Measurement

Four-probe conductivity measurements were performed on sintered pellets at 13 Hz by lock-in detection. The sample dimensions were  $1/2$ " in diameter and 50 mil. in thickness. Four spring-loaded pins arranged in a collinear configuration were pressed against the pellet to serve as the contacts, which were shown to be ohmic from the linearity of the I-V characteristic. To prevent air exposure, the moisture-sensitive sample was covered in a glove box by a lucite cap which also supports the four spring-loaded pins. We calibrated the system by measuring the resistance of a piece of solid molybdenum of the same thickness and diameter as the nitride sample, and a proportionality constant between the resistivity and the resistance of the Mo was obtained (11). This value was then used to convert the resistance to the resistivity for CaNiN. This conversion



assumes that we are measuring the isotropic conductivity of a randomly oriented polycrystalline sample. The temperature dependence of the resistivity from 4 K to 320 K is shown in Fig. 2. The magnitude of the resistivity and the decrease with the decreasing temperature indicate simple metallic behaviour typical of a transition metal compound.

### **Magnetic Susceptibility Measurement**

The Faraday technique was used to measure the magnetic susceptibility of the sample. The susceptibility was measured as a function of the applied field, and it was found to be field dependent, indicating a small contamination by ferromagnetic impurities. The contribution of this ferromagnetic impurity was subtracted from the data by the method of Owen and Honda (12). Assuming that this is due to a very small amount of unreacted nickel, we estimate from the magnitude of this correction that the weight fraction of the unreacted Ni was about 0.05% ( $10^{-4}$ g). The ferromagnetic moment was measured at several different temperatures: 20 K, 100 K, 200 K, and 300 K. The moment had a larger temperature dependence than that of bulk nickel (the percentage change between 20 K and 300 K was four times as large as for bulk nickel). This may be due to a very small particle size of ferromagnetic impurity. Fig. 3 shows the susceptibility corrected for the ferromagnetic impurity from 4 K to 320 K. It is apparent that a temperature dependent paramagnetism remains. This paramagnetism is approximately proportional to  $1/T$  at high temperatures and saturates near 7 K (Fig. 4), indicating an antiferromagnetic ordering. Assuming that each Ni has  $s=1/2$  and  $g=2$ , we find that only 5% of the Ni

would have a magnetic moment by fitting the data with the Curie-Weiss law at high temperatures. There are two possibilities for the origin of this small paramagnetic contribution: it is intrinsic to the material so that each Ni has a small moment of 0.39 Bohr magnetons, or it is due to a small amount of paramagnetic impurities in the CaNiN. If the impurity were Fe with a moment of 5.9 Bohr magnetons, then about 0.5% Fe would be required, but this seems a little high. Only microscopic measurements can determine the origin of this moment unambiguously. Finally, a constant paramagnetic susceptibility is obtained when the data are extrapolated to infinite temperature. This susceptibility is assumed to be intrinsic to the sample and has the value  $(64 \pm 10) \times 10^{-6}$  emu/mole.

### Discussion

In CaNiN, the shortest Ni-Ni distance of 3.50 Å is much longer than the Ni-Ni distance of 2.49 Å in nickel metal, indicating very weak Ni-Ni interactions. However, the Ni-N distance, 1.79 Å, is shorter than the Ca-N distance, 2.51 Å; substantial bonding between the nickel and the nitrogen in CaNiN is obvious. In the solid solution  $\text{Li}_{3-x}\text{Ni}_x\text{N}$  ( $x < 0.6$ ) the nickel replaces some of those lithium atoms bonded to two nitrogen atoms in  $\text{Li}_3\text{N}$  (13). The nickel in that phase is therefore also linearly coordinated to two nitrogen atoms. The Ni-N distance in CaNiN is within the range of variation of the Ni-N bond length of that compound, from 1.91 Å to 1.76 Å as  $x$  goes from 0.1 to 0.6. The Ca-N distance, 2.51 Å, in CaNiN is close to the average value, 2.47 Å, in  $\text{Ca}_3\text{N}_2$  (14). The Ca-Ni distances in the intermetallic compounds  $\text{CaNi}_2$  and  $\text{CaNi}_5$  are 3.01 Å and 3.00 Å

respectively (15), which are also close to the Ca-Ni distance of 3.04 Å in this nitride.

Two interesting features of this compound are the octahedrally coordinated nitrogen and the ----Ni-N-Ni-N---- linear chains. In the ternary calcium nitrides so far examined, the nitrogen is coordinated by six metal atoms that form a (distorted) octahedron about the nitrogen. Examples are the anti-perovskite  $\text{Ca}_3\text{XN}$  ( $\text{X}=\text{Bi}, \text{Sb}, \text{As}, \text{P}, \text{Pb}, \text{Sn}, \text{Ge}$ ) (16),  $\text{Ca}_2\text{ZnN}_2$  (17),  $\text{Ca}_{1-x}\text{Ti}_x\text{N}$  (18), the intermetallic compound  $\text{Ca}_4\text{In}_2\text{N}$  (19), and  $\text{CaGaN}$  (20). Quasi-one dimensional compounds often exhibit interesting physical properties such as charge density waves or a Peierls distortion (21). But we did not observe any anomaly in either the conductivity or the magnetic susceptibility from 4 K to 320 K.

Although this compound has a simple structure with atoms in special positions, it is uncommon. The same structure type has been found only in  $\text{YCoC}$  (22) and  $\text{SrLiN}$  (23). The band structure of  $\text{YCoC}$  has been previously reported (24). Without any significant change we can apply the band structure for  $\text{YCoC}$  to  $\text{CaNiN}$  (25). Assuming that calcium is so electropositive that it is taken as  $2^+$ , the total number of electrons per  $(\text{NiN})^{2-}$  unit is 17. We take the direction of the chain as the  $z$  direction. The  $P_z$  orbital of nitrogen interacts with the  $d_{z^2}$  orbital of nickel to form bonding  $\sigma$  and anti-bonding  $\sigma^*$  bands. The  $p_x$  and  $p_y$  orbitals of nitrogen have  $\pi$  interactions with the  $d_{xz}$  and  $d_{yz}$  orbitals of nickel respectively; the  $d_{xy}$  and  $d_{x^2-y^2}$  orbitals of nickel do not participate in bonding. The  $\sigma^*$  band has the highest energy, the  $\pi^*$ ,  $d_{xy}$ ,  $d_{x^2-y^2}$ ,  $\pi$  and bands reside in the middle, and the  $\sigma$  band has the lowest energy. The 17 electrons then fill these 8 bands and a lower band derived from the nitrogen  $s$  orbital. Since the bands can accommodate 18 electrons, the Fermi level lies in a partially

filled  $\sigma^*$  band, and CaNiN is thus expected to be metallic as observed. However, these bands are very one dimensional because the dispersion perpendicular to the chain direction is very small (0.2 eV perpendicular to chain compared to 1.5 eV along the chain for the conduction band). The lack of a Peierls distortion is therefore puzzling.

### Summary

We have observed metallic behavior in CaNiN. Due to small amounts of paramagnetic impurity, we obtain only an approximate value for the temperature independent paramagnetic susceptibility of CaNiN. The origin of the temperature dependent susceptibility is uncertain, but is likely due to an impurity at the 0.5% level. It would be interesting to grow single crystals to explore the anisotropy in properties and for more accurate measurements. In CaNiN the oxidation state of the nickel is  $1^+$ , and the electronic configuration for Ni (I) is  $d^9$ . In high temperature superconductors copper has a  $d^9$  configuration. One of our current efforts is to further study the nickel nitride chemistry to see if analogues of the copper oxides can be obtained.

## **Acknowledgement**

We would like to thank Marc Hornbostel for assistance with the Faraday measurements. We are indebted to Dr. Donald Czechowicz of Los Alamos National Laboratory for helping us in the design of the modified Dumas apparatus for nitrogen analysis; the construction and calibration of this apparatus by Abby Wizansky and Deborah Vennos are greatly appreciated. We are grateful for support of this work by the Office of Naval Research.

## References

1. F. K. Patterson and R. Ward, *Inorg. Chem.* **5**, 1312 (1966).
2. R. Karam and R. Ward, *Inorg. Chem.* **9**, 1849 (1970).
3. J. P. Motte and R. Streiff, *Compt. Rend.* **267C**, 1598 (1968).
4. R. Juza and W. Sachsze, *Z. Anorg. Allg. Chem.* **251**, 201 (1943).
5. K. H. Jack, *Acta Crystallogr.* **3**, 392 (1950).
6. A. Westgren, *Z. Anorg. Allg. Chem.* **239**, 82 (1938).
7. J. B. Parise, *Acta Crystallogr.* **B36**, 1179 (1980).
8. to be published.
9. G. M. Gustin and C. L. Ogg, in *Treatise on Analytical Chemistry*, Part II, *Analytical Chemistry of Inorganic and Organic Compounds*, Vol 11, P 405, edited by I. M. Kolthoff and P. J. Elving, (Wiley Interscience, 1965).
10. K. Yvon, W. Jeitschko, and E. Parthé, *J. Appl. Crystallogr.* **10**, 73 (1977).
11. J. D. Wasscher, *Philips Res. Rep.* **16**, 301 (1961).
12. P. W. Selwood, *Magnetochemistry*, P 186, (Wiley Interscience, 1979).
13. V. W. Sachsze and R. Juza, *Z. Anorg. Allg. Chem.* **259**, 278 (1949).
14. Y. Laurent, J. Lang, and M. T. LeBihan, *Acta Crystallogr.* **B24**, 494 (1968).
15. *Pearson's Handbook of Crystallographic Data for Intermetallic Phases*, edited by P. Villars and L. D. Calvert, (American Society for Metals, 1985).
16. to be published.
17. to be published.
18. to be published.

19. G. Cordeied and S. Rönninger, *Z. Naturforsch* **42b**, 825 (1987).
20. P. P. Verdier, P. L'Haridon, and M. Marchand, *Acta Crystallogr.* **B30**, 226 (1974).
21. F. J. DiSalvo and T. M. Rice, *Phys. Today* **32**, No 4, 32 (1979).
22. M. H. Gerss and W. Jeitschko, *Z. Naturforsch* **41b**, 946 (1989).
23. G. Cordier, A. Gudat, R. Kniep, and A. Rabenau, *Angew. Chem. Int. Ed. Engl.* **2**, 28 (1989).
24. R. Hoffmann, J. Li, R. A. Wheeler, *J. Amer. Chem. Soc.* **109**, 6600 (1987).
25. J. Li, private communication.

## Figure Captions

- Figure 1.** Crystal structure of CaNiN. The unit cell is drawn by the full lines. The nickel and the nitrogen atoms are connected by the bold lines. The dashed lines connecting Ca-N and Ca-Ni show that calcium is tetrahedrally coordinated by nitrogen, and that nitrogen is in the octahedral hole surrounded by two nickel and four calcium atoms.
- Figure 2.** Temperature dependence of the resistivity of CaNiN.
- Figure 3.** Temperature dependence of the magnetic susceptibility of CaNiN, after a small contribution from the ferromagnetic impurity has been subtracted.
- Figure 4.** The susceptibility of the sample is observed to saturate below 7 K.



TABLE I

X-RAY POWDER DIFFRACTION DATA  
 $(\lambda_{\text{CuK}\alpha_1} = 1.540560 \text{ \AA})$  FOR CANIN

<i>hkl</i>	$d_{\text{obs}}$ (Å)	$d_{\text{calc}}$ (Å)	$I/I_{0,\text{obs}}$	$I/I_{0,\text{calc}}$
100	3.0928	3.0928	3	2
002	3.5050	3.5048	6	5
101	3.1884	3.1889	5	4
*	2.7818		1	
110	2.5320	2.5321	38	39
102	2.5048	2.5047	100	100
*	2.4117		3	
112	-	2.0525	<1	<1
103	1.9568	1.9568	1	1
200	1.7902	1.7905	20	21
004	1.7525	1.7524	10	10
201	-	1.7348	<1	<1
*	1.7064	-	1	-
210	-	1.6014	-	0
202	1.5942	1.5944	1	1
104	-	1.5740	<1	<1
211	-	1.5612	<1	<1
212	1.4566	1.4566	29	32
114	1.4409	1.4410	11	12
203	-	1.4212	-	0
213	-	1.3210	<1	<1
105	-	1.3054	<1	<1
220	1.2660	1.2661	5	6
204	1.2524	1.2524	10	11
300	-	1.1936	<1	<1
222	-	1.1907	<1	<1
214	-	1.1822	<1	<1
301	-	1.1767	<1	<1
006	-	1.1683	<1	<1
310	1.1327	1.1324	4	5
302	1.1302	1.1299	6	7
311	-	1.1179	-	0
106	1.1103	1.1106	6	6
205	-	1.1038	-	0

TABLE I -- continued

<i>hkl</i>	$d_{\text{obs}}$ (Å)	$d_{\text{calc}}$ (Å)	$I/I_{0,\text{obs}}$	$I/I_{0,\text{calc}}$
312	-	1.0775	<1	<1
303	-	1.0630	<1	<1
116	-	1.0608	<1	<1
215	-	1.0548	<1	<1
224	1.0261	1.0262	6	6
313	-	1.0190	-	0
320	-	0.9932	<1	<1
304	-	0.9865	<1	<1
321	-	0.9834	<1	<1
206	-	0.9784	<1	<1
107	-	0.9644	<1	<1
322	0.9556	0.9556	7	9
314	0.9511	0.9512	4	7

\* Impurity lines due to CaO

TABLE II  
INTERATOMIC DISTANCES FOR CANIN

---

Ni-Ni <sup>a</sup>	3.5809Å	Ni-Ni <sup>b</sup>	3.5048Å
Ni-N	1.7904Å	Ca-N	2.5053Å
Ni-Ca	3.0352Å		

---

<sup>a</sup> Distance between parallel chains.

<sup>b</sup> Distance between perpendicular chains.


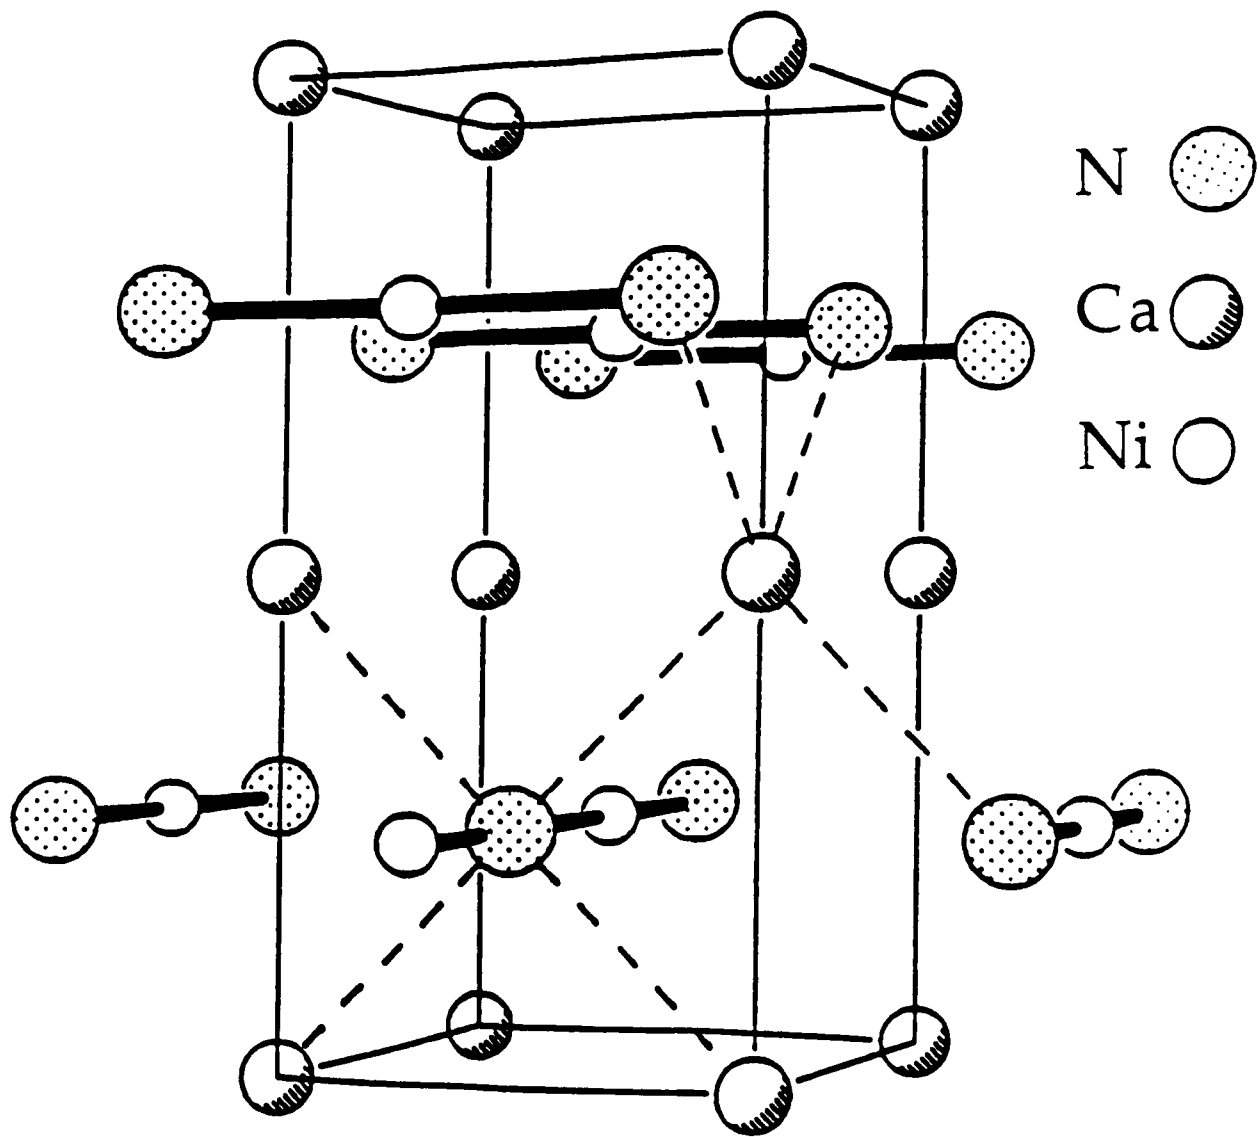



Fig 1

Resistivity ( $10^{-6}$  Ohm-cm)

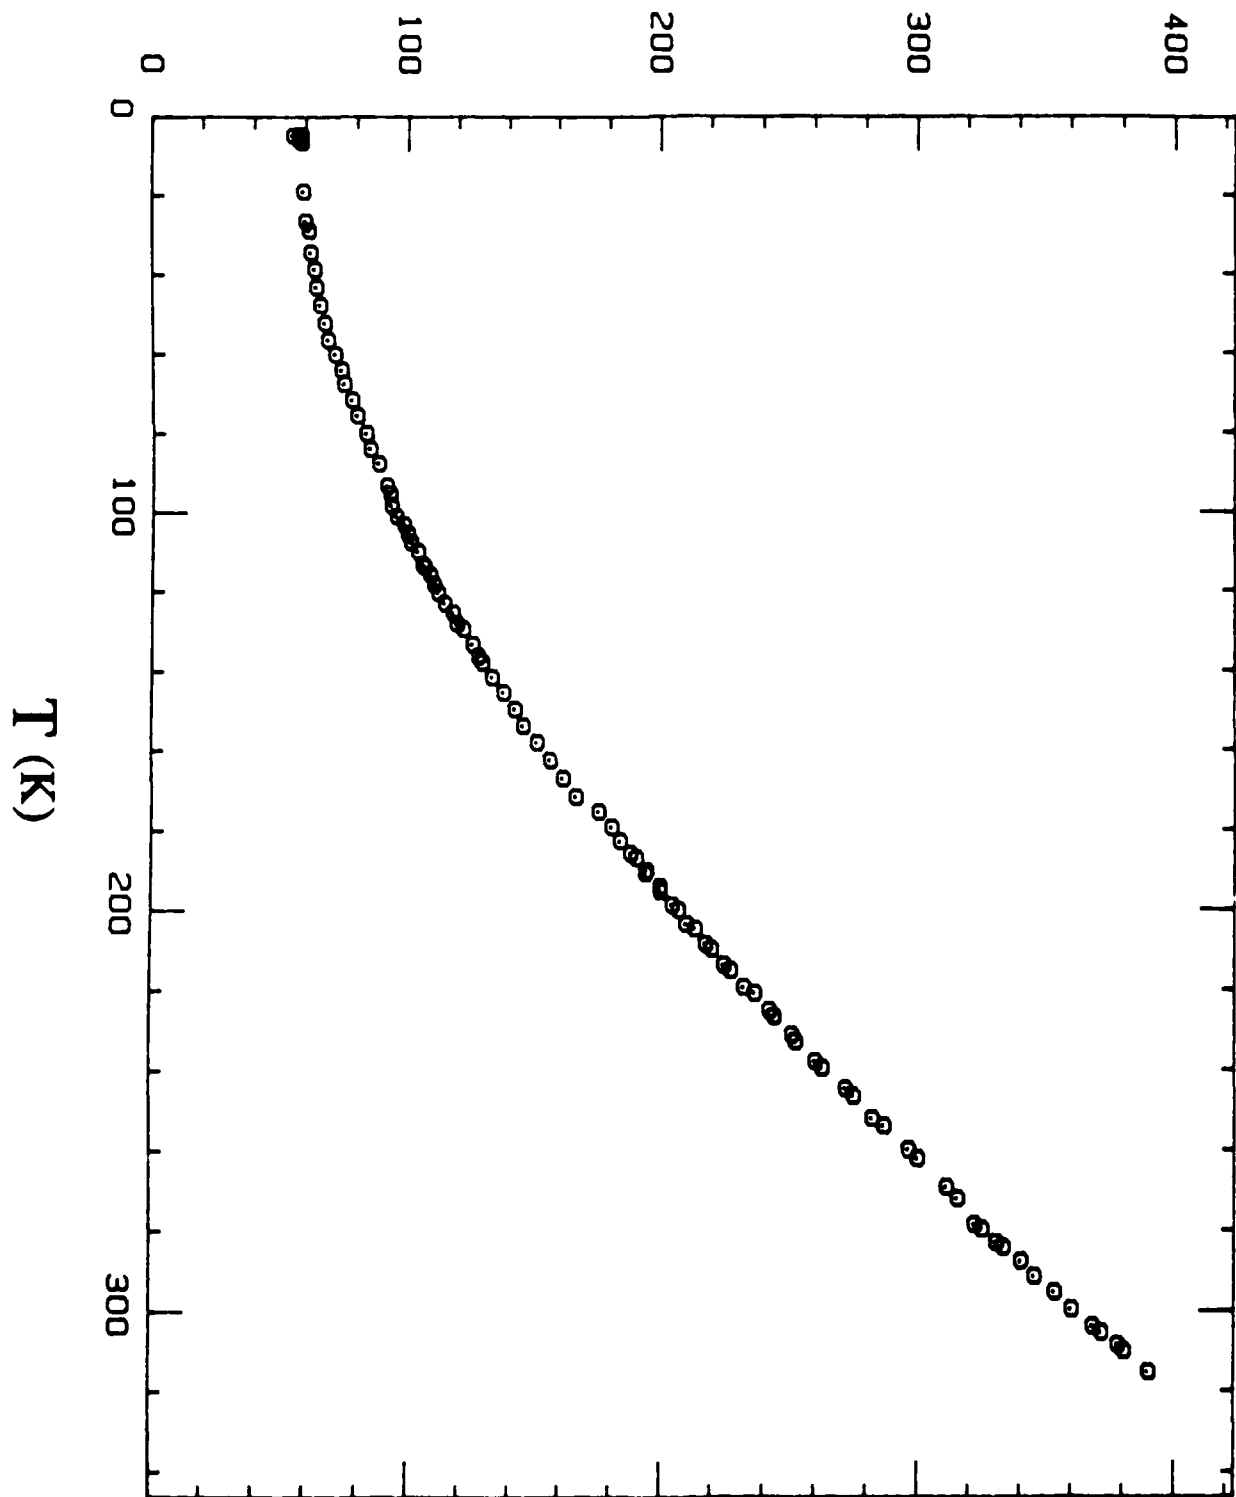

11/11

$\chi_M$  ( $10^{-6}$  emu / mole)

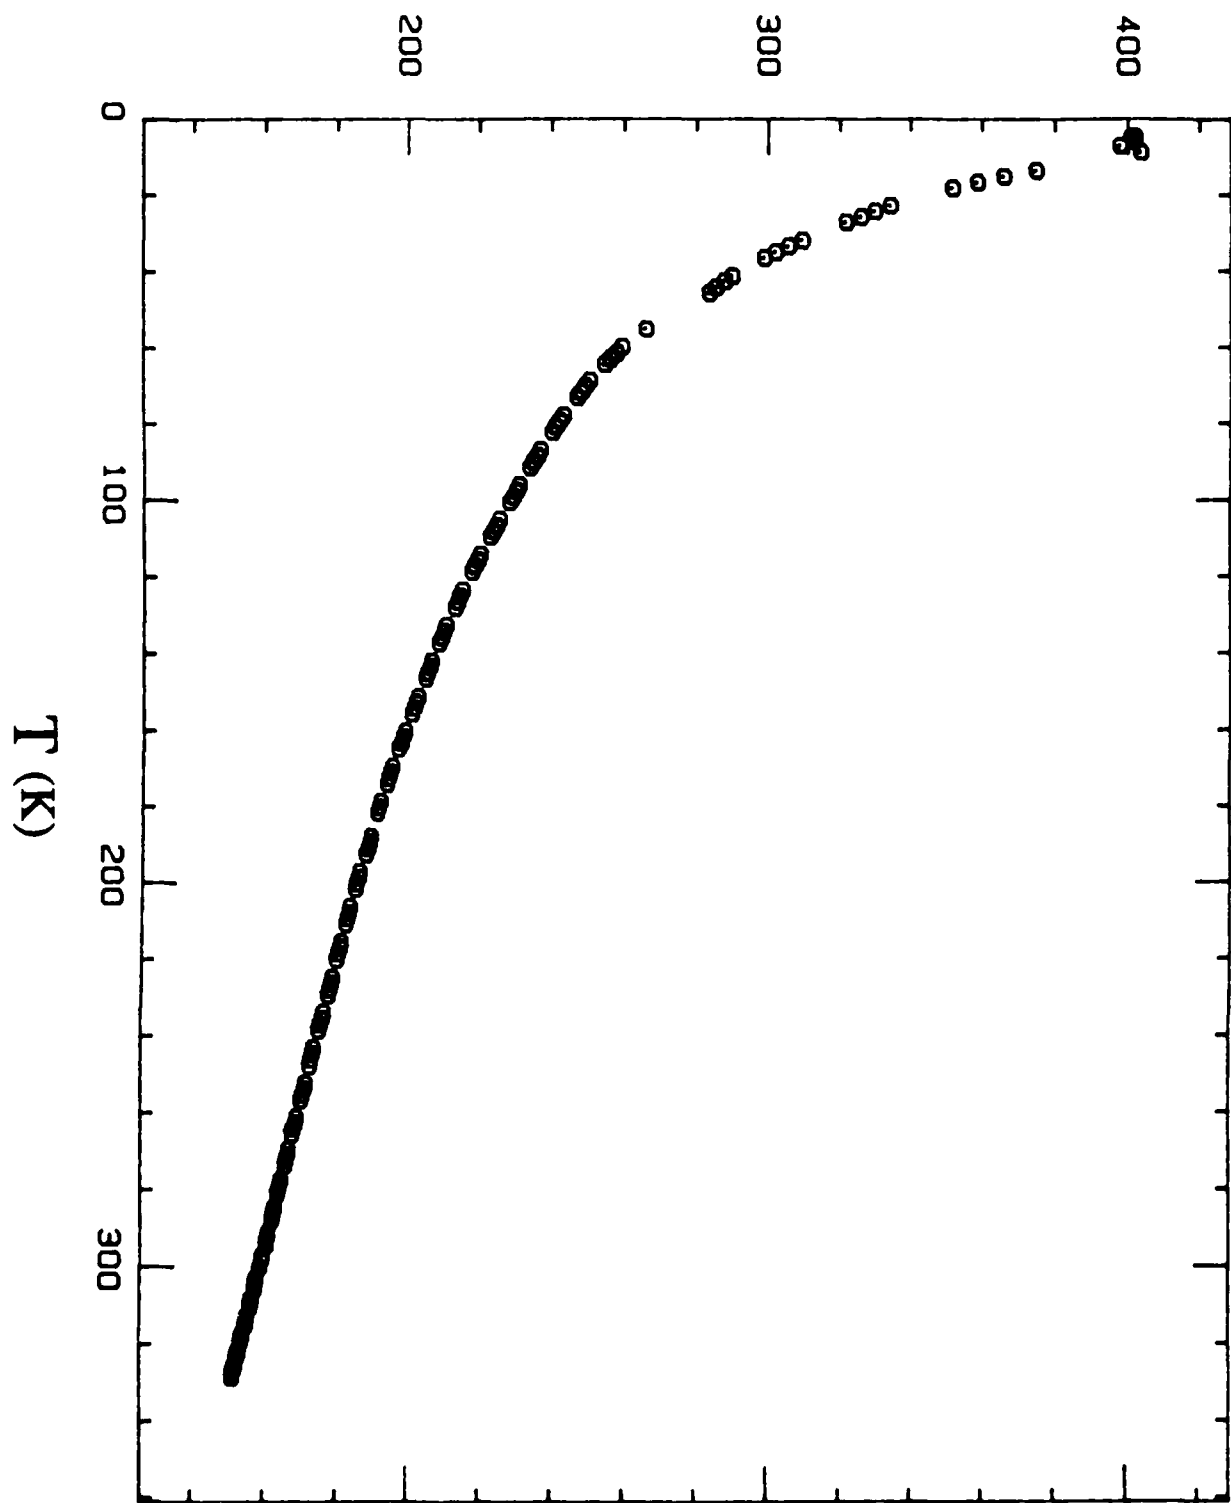

$\chi_M (10^{-6} \text{ emu / mole})$

