

2

DWG FILE

OFFICE OF NAVAL RESEARCH

CONTRACT NOOO 14-89-J-1849

R & T Code 4134005

Technical report No. 11

PREPARATION AND CHARACTERIZATION OF DISPERSED "COBALT OXIDE" SUPPORTED ON γ -Al₂O₃

by

C-S. Bai, S. Soled, K. Dwight and A. Wold

AD-A231 269

Prepared for Publication in
JOURNAL OF SOLID STATE CHEMISTRY

December 21, 1990

Brown University
Department of Chemistry
Providence, Rhode Island 02912

SDTIC
ELECTE
JAN 23 1991
S E D

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

67

REPORT DOCUMENTATION PAGE

1a REPORT SECURITY CLASSIFICATION unclassified		1b RESTRICTIVE MARKINGS	
2a SECURITY CLASSIFICATION AUTHORITY		3 DISTRIBUTION/AVAILABILITY OF REPORT APPROVED FOR PUBLIC RELEASE DISTRIBUTION UNLIMITED	
2b DECLASSIFICATION/DOWNGRADING SCHEDULE			
4 PERFORMING ORGANIZATION REPORT NUMBER(S) Report No. 11		5 MONITORING ORGANIZATION REPORT NUMBER(S) N000 14-89-J-1849	
6a. NAME OF PERFORMING ORGANIZATION BROWN UNIVERSITY AARON WOLD	6b OFFICE SYMBOL (if applicable)	7a. NAME OF MONITORING ORGANIZATION OFFICE OF NAVAL RESEARCH CODE 427 1113	
6c. ADDRESS (City, State, and ZIP Code) DEPARTMENT OF CHEMISTRY Box H BROWN UNIVERSITY PROVIDENCE, RI 02912		7b. ADDRESS (City, State, and ZIP Code) DR. MARK ROSS 800 N. Quincy St. Arlington, VA 22217	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION	8b. OFFICE SYMBOL (if applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER	
8c. ADDRESS (City, State, and ZIP Code)		10 SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO.	PROJECT NO.
		TASK NO.	WORK UNIT NO.
11. TITLE (Include Security Classification) PREPARATION AND CHARACTERIZATION OF DISPERSED "COBALT OXIDE" SUPPORTED ON γ -Al ₂ O ₃			
12. PERSONAL AUTHOR(S) C-S. Bai, S. Soled, K. Dwight and A. Wold			
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM _____ TO _____	14 DATE OF REPORT (Year, Month, Day) Dec. 21, 1990	15 PAGE COUNT
16 SUPPLEMENTARY NOTATION Prepared for publication in Journal of Solid State Chemistry			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	
19. ABSTRACT (Continue on reverse if necessary and identify by block number) Samples of "cobalt oxide" supported on gamma-Al ₂ O ₃ were prepared from a variety of precursors. The samples were characterized by x-ray analysis, temperature programmed reduction, and measurement of magnetic susceptibility. Their properties were compared with those of bulk Co ₃ O ₄ and CoAl ₂ O ₄ and the observed differences were related to the method of preparation.			
20 DISTRIBUTION/AVAILABILITY OF ABSTRACT <input type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21 ABSTRACT SECURITY CLASSIFICATION	
22a NAME OF RESPONSIBLE INDIVIDUAL		22b TELEPHONE (Include Area Code)	22c OFFICE SYMBOL

PREPARATION AND CHARACTERIZATION OF

DISPERSED "COBALT OXIDE" SUPPORTED ON γ -Al₂O₃

C-S. Bai, S. Soled*, K. Dwight and A. Wold

Department of Chemistry, Brown University

Providence, Rhode Island 02912

*Exxon Research & Engineering

Annandale, New Jersey 08801



Accession For	
NTIS	<input checked="" type="checkbox"/>
GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

Abstract

Samples of "cobalt oxide" supported on $\gamma\text{-Al}_2\text{O}_3$ were prepared from a variety of precursors. The samples were characterized by x-ray analysis, temperature programmed reduction, and measurement of magnetic susceptibility. Their properties were compared with those of bulk Co_3O_4 and CoAl_2O_4 and the observed differences were related to the method of preparation.

Introduction

The nature of cobalt catalysts supported on $\gamma\text{-Al}_2\text{O}_3$ has been the subject of many investigations (1-17). Most of these studies were concerned with the role of cobalt in hydrocracking processes and tried to provide an understanding of hydrodesulfurization of fossil fuels. During the final heat treatment in the preparation of these catalysts, cobalt ions diffuse into the $\gamma\text{-Al}_2\text{O}_3$ structure and can occupy octahedral or tetrahedral sites. In most studies (1-17) it was reported that a dispersed " δ -phase" predominates when the cobalt loading is less than 2%. This phase consists of Co(II) ions and shows many of the chemical features of bulk CoAl_2O_4 . This phase contains "non-reducible" cobalt. A second β -phase occurs at higher cobalt loading, and consists of Co_3O_4 crystallites which can be reduced easily.

In almost all of the above studies, the precursor used to prepare the $\gamma\text{-Al}_2\text{O}_3$ supported cobalt samples was an aqueous solution of cobalt nitrate. However, the literature does not include any systematic study of the influences of the precursor compound or the pH of the precursor solution on the dispersion of cobalt on $\gamma\text{-Al}_2\text{O}_3$.

In the present study, various precursors are used to prepare γ - Al_2O_3 samples containing "cobalt oxide." Each precursor is dissolved in an aqueous solution at a known pH. X-ray analysis, temperature programmed reduction studies and magnetic susceptibility measurements are used to characterize the composition and properties of each supported cobalt oxide sample.

Experimental

Preparation of samples. Bulk Co_3O_4 was prepared by the decomposition of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (Mallinckrodt) at 450°C for 24 hours. CoAl_2O_4 was synthesized by dissolving appropriate weights of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and $\text{Al}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ (Allied Chemical) in water, evaporating to dryness, followed by careful decomposition of the product at 450°C . The resulting mixed oxides were heated in air at 950°C for 24 hours. CoO was prepared by heating CoCO_3 (Allied Chemical) at 1000°C in an argon atmosphere for 24 hours. The γ - Al_2O_3 was prepared by heating boehmite at 500°C in air for 24 hours. Boehmite (γ - AlOOH) was prepared hydrothermally according to the procedure of A. B. Kiss (18).

Samples of cobalt oxide containing 11.29 weight percent cobalt supported on γ - Al_2O_3 were prepared from various cobalt precursors, namely, cobalt

acetate, cobalt nitrate, cobalt citrate and cobalt acetylacetonate. The latter two compounds were prepared in this laboratory. Analyses for the actual compositions of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ and $\text{Co}(\text{C}_2\text{H}_3\text{O}_2)_2 \cdot 4\text{H}_2\text{O}$ were performed by heating representative samples in air to 500°C and obtaining the weight loss. Corrected values reduced the compositions of cobalt dispersed on $\gamma\text{-Al}_2\text{O}_3$ samples from a nominal 11.38 weight percent cobalt to 11.29 weight percent. The products Co_3O_4 , CoO and CoAl_2O_4 were confirmed by x-ray analysis, temperature programmed reduction and magnetic susceptibility measurements; the phase $\gamma\text{-Al}_2\text{O}_3$ was confirmed by x-ray diffraction analysis. An aqueous solution of each cobalt precursor was prepared and the pH was adjusted with acid. The acid was usually chosen to have the same anion as the precursor (see Table 1). $\gamma\text{-Al}_2\text{O}_3$ was impregnated with the precursor solution, dried on a hot plate, and then heated in a drying oven at 230°C for 24 hours. The final heat treatment was carried out at 450°C for 24 hours.

Characterization of samples. X-ray powder diffraction analyses of the samples were obtained using a Philips diffractometer and monochromatic high intensity $\text{CuK}\alpha_1$ radiation ($\lambda = 1.5405 \text{ \AA}$). The diffraction patterns were taken

in the range of $12^\circ < 2\theta < 72^\circ$ with a scan rate of $1^\circ 2\theta/\text{min}$ and a chart speed of 30 in/hr.

Magnetic susceptibility was measured with a Faraday balance at a field strength of 10.4 kOe from liquid nitrogen temperature to 700 K. Honda-Owens (field dependency) measurements (susceptibility vs $1/H$) were also made at room temperature and liquid nitrogen temperature, and all magnetic susceptibility data were corrected for core diamagnetism.

Temperature programmed reduction (TPR) measurements were taken using a Cahn system 113 thermal balance. The samples impregnated on $\gamma\text{-Al}_2\text{O}_3$ were preheated in air at 400°C for 4 hours to remove most of the residual water before reduction. However, to correct for all of the residual water, a sample of $\gamma\text{-Al}_2\text{O}_3$ was heated in dry air to 950°C and its weight loss was used to correct the initial sample weights. This correction amounted to approximately one third of the total weight loss of a fully reduced sample of $\gamma\text{-Al}_2\text{O}_3$ impregnated with 11.29 weight percent cobalt. The samples were cooled down to room temperature and were then heated at $60^\circ\text{C}/\text{hr}$ from room temperature to 950°C in a purified Ar/H_2 (85/15) atmosphere; the rate of gas flow was 60 ml/min. The samples were maintained at 950°C for 4 hours in order to ensure constant weight. Two samples, i.e. CoAl_2O_4 and the cobalt oxide, dispersed on

γ - Al_2O_3 , which was prepared from a cobalt acetate precursor at pH 2.7, were heated in pure hydrogen at 950°C until ~ 99% of the cobalt was reduced to cobalt metal.

Results and Discussion

The bulk standard, Co_3O_4 , was prepared by the decomposition of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ at 450°C in air for 24 hours. X-ray diffraction analysis of the product confirmed the presence of Co_3O_4 . Temperature programmed reduction of the product was carried out under an atmosphere of Ar/ H_2 (85/15) from room temperature to 950°C. For the standard Co_3O_4 sample, reduction commenced at 220°C and was complete at 320°C. The observed weight loss of 26.6 percent is consistent with a calculated value of 26.5 weight percent for the reduction of Co_3O_4 to cobalt metal. These results are in agreement with those previously reported in the literature (19).

However, bulk CoAl_2O_4 showed no appreciable reduction in an Ar/ H_2 (85/15) atmosphere when heated up to 320°C. The product was then heated from 320°C to 950°C and maintained in the reducing atmosphere at 950°C for a total of four hours in order to achieve constant weight. The observed weight loss of 8.37 percent corresponds to 92.5 percent of the calculated value for the reducible

cobalt present. Reduction of CoAl_2O_4 in a pure hydrogen atmosphere at 950°C resulted in the reduction of 98.7 percent of the total reducible cobalt (see Table 2), because of the greater reducing power of pure hydrogen compared with that of Ar/H_2 (85/15).

X-ray analysis of the reduction products formed from bulk CoAl_2O_4 , which had been reduced at a maximum temperature of 950°C , indicated the presence of metallic cubic cobalt, and $\alpha\text{-Al}_2\text{O}_3$. These results are consistent with the temperature programmed reduction data given in Table 2.

The sample of "cobalt oxide" supported on $\gamma\text{-Al}_2\text{O}_3$, prepared from the cobalt nitrate precursor at $\text{pH} = 2.7$, contained 11.29 weight percent of cobalt. This sample when formed at 450°C was identified by x-ray analysis as $\text{Co}_3\text{O}_4 + \gamma\text{-Al}_2\text{O}_3$ (see Table 3). Magnetic susceptibility data (Table 4) confirmed the presence of the oxide Co_3O_4 . This sample was reduced in an atmosphere of Ar/H_2 (85/15) and at 320°C the observed weight loss of 0.97% corresponds to the calculated value for the reduction of all the Co(III) to Co(II) (Table 2). There was no evidence of free cobalt metal in the product. From magnetic susceptibility measurements of the product reduced at 320°C , the moment of the cobalt, namely 4.2 BM, corresponded to the value for Co(II) in a tetrahedral environment (20).

From Table 2 it can be seen that the additional weight loss between 320-950°C was 2.69 percent, which is 91% of the value calculated for the complete reduction of all the cobalt(II). The cobalt reduced in this temperature range is referred to as "fixed cobalt(II) in a tetrahedral oxide environment." This cobalt species is similar in its property towards reduction to the cobalt(II) in CoAl_2O_4 .

The sample of cobalt oxide supported on $\gamma\text{-Al}_2\text{O}_3$ prepared from the nitrate precursor at pH = 5.6 showed little change from that prepared at pH = 2.7. Undoubtedly, the formation of a considerable quantity of Co_3O_4 is a result of the partial oxidation of Co(II) by the nitrate ion, particularly during decomposition of the nitrate precursor.

For the samples prepared from cobalt acetate as a precursor at pH = 2.7, the TPR results shown in Table 2 indicate that most of the cobalt oxide is fixed and only a small quantity of Co_3O_4 is present in the final product. The x-ray results confirmed these observations. When the pH of the cobalt acetate was raised to 5.6, there was an observed increase in the Co_3O_4 content and a corresponding reduction in the amount of initial "fixed cobalt."

The magnetic susceptibility measurements are summarized in Table 4. The susceptibilities for bulk samples of Co_3O_4 and CoAl_2O_4 were determined to be 2.8 BM/mol Co and 4.2 BM/mol Co, respectively. The values for μ , given in Table 4, for the products obtained from the decomposition of the acetate, acetylacetonate and citrate precursors are consistent with the relative quantity of fixed cobalt present in the samples, as obtained by TPR studies (Table 2).

For the products obtained from the nitrate precursor there appears to be a discrepancy between the susceptibility data and the TPR results. The μ values indicate that almost all of the cobalt is present as Co_3O_4 , whereas the TPR results show the apparent formation of a large amount of fixed cobalt oxide during the initial stage of the reduction process. Fig. 1 characterizes the reduction of bulk Co_3O_4 and 11.29 weight percent cobalt on $\gamma\text{-Al}_2\text{O}_3$ (from the nitrate precursor at pH = 2.7) in an oscillating magnetic field. The observed change in weight, therefore, measures the relative quantity of metallic cobalt formed during the reduction process. It can be seen that whereas bulk Co_3O_4 reduces immediately to cobalt metal at 290°C, the supported samples produce no metallic cobalt until 420°C. This indicates that the initial stage of the reduction process involves the reduction of

cobalt(III) to cobalt(II) which behaves then as tetrahedral cobalt in an oxide environment. Hence, for all of the supported cobalt samples reduced between 220-320°C, the reduction process can be represented as a change of Co(III) to Co(II).

Acknowledgments

This research has been partially supported by the Office of Naval Research and by the National Science Foundation, Contract No. DMR 880-3184.

References

1. F. E. Massoth, "Advances in Catalysis," Vol. 27, P. 265, Academic Press, New York, 1978.
2. M. Lo Jacono, A. Cimino, and G. C. A. Schuit, *Gazz. Chim. Ital.*, 103, 1281 (1973).
3. J. R. Tomlinson, R. O. Keeling, G. T. Rymer, and J. M. Bridges, "Actes du 2me Congr. Int. Catal." p. 1831. Editions Technip. Paris, 1961.
4. J. H. Ashley, and P. C. H. Mitchell, *J. Chem. Soc. A*, 2730 (1969).
5. H. Ueda, and N. Todo, *J. Catal.*, 27, 281 (1972).
6. M. Lo Jacono, J. L. Verbeek, and G. C. A. Schuit, *J. Catal.*, 29, 463 (1973).
7. P. Ratnasamy, A. V. Ramaswamy, K. Banerjee, D. K. Sharma, and N. Ray, *J. Catal.*, 38, 19 (1975).

8. J. Grimbolt, J. P. Bonnelle, and J. P. Beaufils, *J. Electron. Spectrosc. Relat. Phenom.*, 8, 437 (1976).
9. R. I. Declerck-Grimée, P. Caresson, R. M. Friedman, and J. J. Fripiat, *J. Phys. Chem.*, 83, 885 (1978).
10. H. Topsøe, B. S. Clausen, N. Burriesci, R. Candia, and S. Mørup, in "Preparation of Catalysts, II" (B. Delmon, P. Grange, P.A. Jacobs and G. Poncelet, Eds.), p. 479. Elsevier, Amsterdam, 1979.
11. A. Lycourghiotis, C. Defossé, F. Delannay, J. LeMaitre, and B. Delmon, *J. Chem. Soc. Faraday Trans. 1*, 76, 1677 (1980).
12. R. B. Gregor, F. W. Lytle, R. L. Chin, and D. M. Hercules, *J. Phys. Chem.*, 85, 1232 (1981).
13. K. S. Chung, and F. E. Massoth, *J. Catal.*, 64, 320 (1980).
14. R. L. Chin, and D. M. Hercules, *J. Phys. Chem.*, 86, 360 (1982).
15. K. S. Chung, and F. E. Massoth, *J. Catal.*, 64, 332 (1980).
16. N. Y. Topsøe, and H. Topsøe, *J. Catal.*, 75, 354 (1982).
17. P. Arnoldy, and J. A. Moulign, *J. Catal.*, 93, 38 (1985).
18. A. B. Kiss, G. Keresztuny, and L. Farkas, *Spectrochimica Acta*, 36A, 653 (1980).
19. P. Wu, R. Kershaw, R. Dwight, and A. Wold, *Mat. Res. Bull.*, 23, 475 (1988).
20. P. Cossee, "Magnetic Properties of Cobalt in Co_3O_4 and Other Oxides." Ph.D. Thesis, University of Leiden, Holland, 1956.

Figure Caption Sheet

Fig. 1. Variation of weight with application of a magnetic field as a function of temperature for supported "cobalt oxide" prepared from a cobalt nitrate precursor compared with bulk Co_3O_4 .

Magnetic TPR in Ar/H₂

From Nitrate, pH=2.7

Bulk Co₃O₄

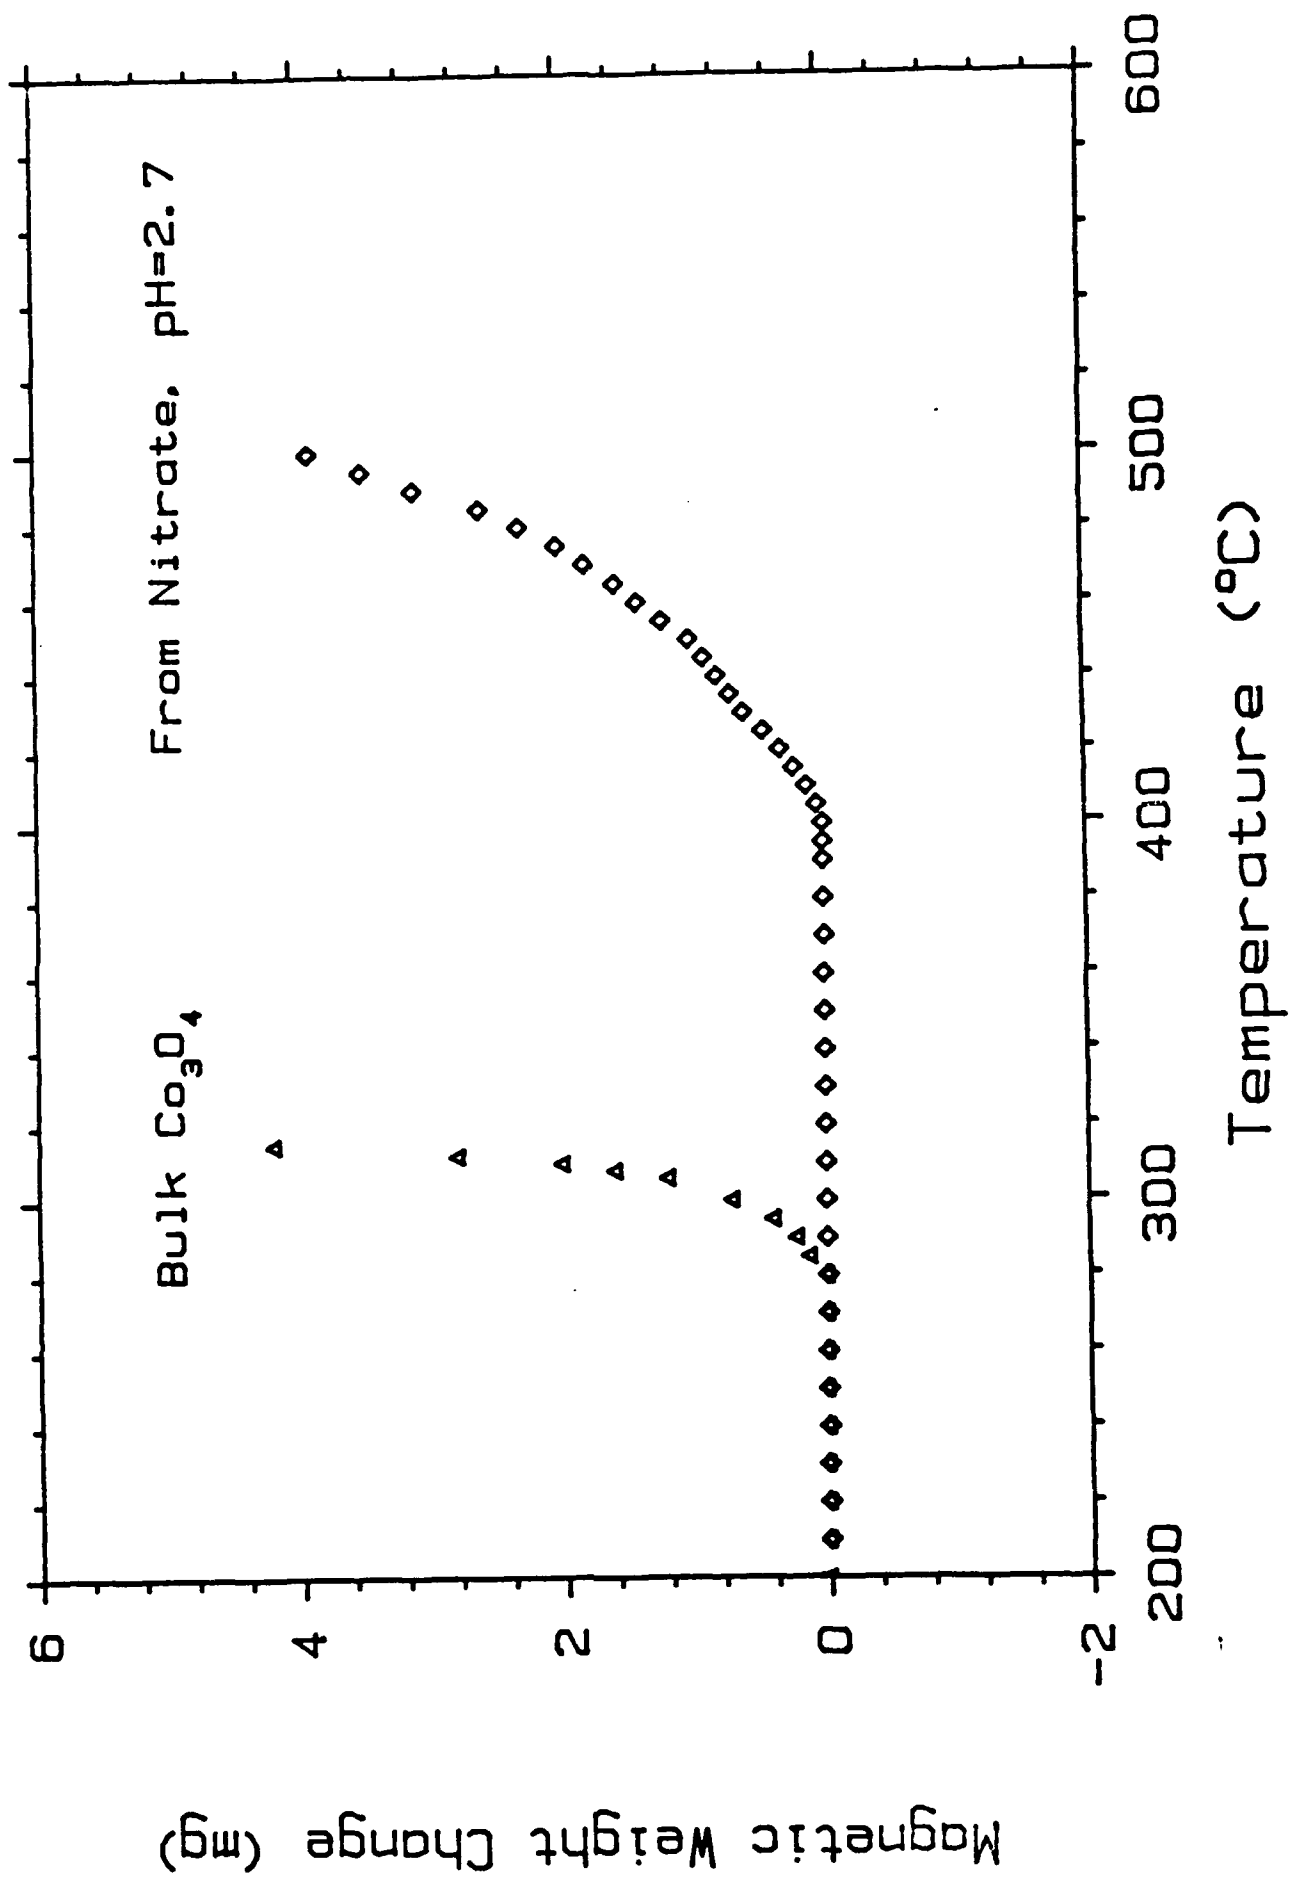


Table 1

Precursors and pH Used To Impregnate the Support $\gamma\text{-Al}_2\text{O}_3$
With 11.29 Weight Percent Cobalt*

Precursor Used	Acid to Adjust pH	pH of Solution
Acetate	HAC	2.7
Acetate	HAC	5.6
Acetylacetonate	HAC	1.9
Citrate	Citric Acid	1.9
Nitrate	HNO_3	2.7
Nitrate	HNO_3	5.6

* Wt% cobalt defined as $100 \times \text{wt}(\text{Co}) / [\text{wt}(\text{Co}) + \text{wt}(\text{Al}_2\text{O}_3)]$

Table 2

Temperature Programmed Reduction Data

for 11.29 Wt% Cobalt* for Various Precursors Supported on γ -Al₂O₃

Samples	Weight Loss (%)		
	320°C	950°C	950°C
	Ar/H ₂	Ar/H ₂	pure H ₂
CoAl ₂ O ₄	0	8.37	8.92(a)
Acetate			
pH = 2.7	0.03	2.72	2.91(b)
pH = 5.6	0.55	2.76	
Acetylacetonate			
pH = 1.9	0.03	2.67	
Citrate			
pH = 1.9	0.06	2.69	
Nitrate			
pH = 2.7	0.97	2.69	
pH = 5.6	0.97	2.69	

* Wt% cobalt defined as $100 \times \text{wt}(\text{Co}) / [\text{wt}(\text{Co}) + \text{wt}(\text{Al}_2\text{O}_3)]$

(a) 98.7% of the value calculated for complete reduction

(b) 98% of the value calculated for complete reduction

Table 3

Phases Formed by 11.29 Wt% Cobalt* from Various Precursors

Dispersed and Decomposed on $\gamma\text{-Al}_2\text{O}_3$

Precursor Samples	Temperature of Decomposition ($^{\circ}\text{C}$)	Phases
Acetate		
pH = 2.7	450	$\gamma\text{-Al}_2\text{O}_3$
pH = 5.6	450	$\text{Co}_3\text{O}_4 + \gamma\text{-Al}_2\text{O}_3$
Acetylacetonate		
pH = 1.9 (in HAC)	450	$\gamma\text{-Al}_2\text{O}_3$
Citrate		
pH = 1.9	450	$\gamma\text{-Al}_2\text{O}_3$
Nitrate		
pH = 2.7	450	$\text{Co}_3\text{O}_4 + \gamma\text{-Al}_2\text{O}_3$
pH = 5.6	450	$\text{Co}_3\text{O}_4 + \gamma\text{-Al}_2\text{O}_3$

* Wt% cobalt defined as $100 \times \text{wt}(\text{Co}) / [\text{wt}(\text{Co}) + \text{wt}(\text{Al}_2\text{O}_3)]$

Table 4
Magnetic Susceptibility Data for 11.29 Wt% Cobalt*
From Various Precursors Supported on γ -Al₂O₃

Samples	μ (BM)/mol Co	θ (K)
Co ₃ O ₄	2.8	-112
CoAl ₂ O ₄	4.2	- 94
Acetate precursor		
pH = 2.7	4.2	- 45
pH = 5.6	3.7	- 47
Acetylacetonate precursor		
pH = 1.9	4.2	- 38
Citrate precursor		
pH = 1.9	3.9	- 44
Nitrate precursor		
pH = 2.7	2.9	- 69
pH = 5.6	2.9	- 66

* Wt% cobalt defined as $100 \times \text{wt}(\text{Co}) / [\text{wt}(\text{Co}) + \text{wt}(\text{Al}_2\text{O}_3)]$