

AD-A235 747

2

Unclassified
SECURITY CLASSIFICATION OF THIS PAGE



REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

1a REPORT SECURITY CLASSIFICATION Unclassified		1b RESTRICTIVE MARKINGS	
2a SECURITY CLASSIFICATION AUTHORITY MAY 23 1991		3 DISTRIBUTION/AVAILABILITY OF REPORT This document has been approved for public release and sale; its distribution is unlimited	
2b DECLASSIFICATION/DOWNGRADING SCHEDULE		5 MONITORING ORGANIZATION REPORT NUMBER(S)	
4 PERFORMING ORGANIZATION REPORT NUMBER(S) ONR-TR 18		7a NAME OF MONITORING ORGANIZATION Office of Naval Research	
6a NAME OF PERFORMING ORGANIZATION Naval Ocean Systems Center	6b OFFICE SYMBOL (if applicable) NOSC	7b ADDRESS (City, State, and ZIP Code) Code 1113, Chemistry Division Arlington, VA 22217	
6c ADDRESS (City, State, and ZIP Code) Code 521 San Diego, CA 92152		9 PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N0001491WX24178	
8a NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research	8b OFFICE SYMBOL (if applicable) ONR	10 SOURCE OF FUNDING NUMBERS	
8c ADDRESS (City, State, and ZIP Code) 800 North Quincy St. Arlington, VA 22217		PROGRAM ELEMENT NO	PROJECT NO
11 TITLE (Include Security Classification) (Unclassified) Laser Action from 2,6,8-Trisubstituted 1,3,5,7-Tetramethylpyrromethene-BF ₂ Complexes: Part 1.		AS- NO	WORK UNIT ACCESSION NO
12 PERSONAL AUTHOR(S) T. G. Pavlopoulos, J. H. Boyer, M. Shah, K. Thangaraj, and M.-L. Soong			
13a TYPE OF REPORT Interim Technical	13b TIME COVERED FROM 06/90 TO 05/91	14 DATE OF REPORT (Year, Month, Day) 91-05-24	15 PAGE COUNT 2
16 SUPPLEMENTARY NOTATION Appl. Optics 29, 3885-3886 (1990)			
17 COSATI CODES		18 SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	Laser dyes, dye lasers, triplet-triplet absorption	
	SUB-GROUP		
19 ABSTRACT (Continue on reverse if necessary and identify by block number)			
Of the four new pyrromethene derivatives studied, 1,3,5,7-pentamethyl-2,6-diethyl-pyrromethene-BF ₂ complex lased about 3 times more efficiently than rhodamine 560 under flashlamp excitation.			
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL Dr. T. G. Pavlopoulos		22b. TELEPHONE (Include Area Code) (619) 553-2792	22c. OFFICE SYMBOL

OFFICE OF NAVAL RESEARCH

Contract N0001491WX24178

R&T Code 4131011

Technical Report No. 18

Laser Action from 2,6,8-Trisubstituted-1,3,5,7-Tetramethyl-
pyrromethene-BF₂ Complex: Part 1

by

T. G. Pavlopoulos, J. H. Boyer, M. Shah,
K. Thangaraj, and M. -L. Soong
Prepared for Publication

in the

Applied Optics 29, 3885 (1990)

Naval Ocean Systems Center
San Diego, CA 92152

24 May 1991

Reproduction in whole or in part is permitted for any purpose of the United States Government

This document has been approved for public release and sale; its distribution is unlimited.



Accession For	
NIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	20

91-00293
110111 110111 110111 110111 110111 110111 110111 110111 110111 110111

7. H. H. Lin, A. Korpel, D. Mehrl, and D. R. Andersen, "Nonlinear Chinese Tea," *Opt. News* 55 (Dec. 1989d).
8. P. W. Smith, J.-P. Hermann, W. J. Tomlinson, and P. J. Maloney, "Optical Bistability at a Nonlinear Interface," *Appl. Phys. Lett.* 35, 846-848 (1979).
9. I. C. Khoo, "Optical-Thermal Induced Total Internal Reflection-to-Transmission Switching at a Glass-Liquid Crystal Interface," *Appl. Phys. Lett.* 40, 645-647 (1982).
10. M. Mohebi, B. Jean-Jean, and J.-C. M. Diels, "Self-Induced Reflection at a Saturable Interface," *Opt. Lett.* 14, 1353-1355 (1989).
11. F. P. Zscheile and C. L. Comar, "Influence of Preparative Procedure on the Purity of Chlorophyll Components as Shown by Absorption Spectra," *Bot. Gaz.* 102, 463-481 (1941).
12. R. C. Weast, Ed., *Handbook of Chemistry and Physics* (CRC Press, Cleveland, 1985-1986), F-4.
13. C. Imbert, "Calculation and Experimental Proof of the Transverse Shift Induced by Total Internal Reflection of a Circularly Polarized Light Beam," *Phys. Rev. D* 5, 787-796 (1972).
14. M. Born and E. Wolf, *Principles of Optics* (Pergamon, London, 1975), p. 627-633.

Laser action from 2,6,8-position trisubstituted 1,3,5,7-tetramethylpyrromethene-BF₂ complexes: part 1

Theodore G. Pavlopoulos, Joseph H. Boyer, Mayur Shah, Kannappan Thangaraj, and Mou-Ling Soong

Theodore Pavlopoulos is with U.S. Naval Ocean Systems Center, Marine Sciences & Technology Department, San Diego, California 92152; the other authors are with University of New Orleans, Chemistry Department, New Orleans, Louisiana 70148.

Received 22 March 1990.

Of the four new pyrromethene derivatives studied, 1,3,5,7,8-pentamethyl-2,6-diethylpyrromethene-BF₂ complex lased ~3 times more efficiently than rhodamine 560 under flashlamp excitation.

For obtaining efficient laser action under flashlamp excitation, the coumarin (blue to yellow/green) and xanthene (yellow to red spectral region) laser dyes are presently the most widely used. Among the xanthene laser dyes, the benchmark of laser dyes in efficiency and photostability is rhodamine 6G. This dye has been known since 1967¹ and was found by trial and error.

Recently, laser action under flashlamp excitation was reported from 1,3,5,7-tetramethylpyrromethene-BF₂ complex 1 (TMP-BF₂) and 1,3,5,7,8-pentamethylpyrromethene-BF₂ complex 2 (PMP-BF₂). TMP-BF₂ lased broadband (BB) somewhat more efficiently than coumarin 545A at 533 nm,² and PMP-BF₂ lased BB ~3 times more efficiently than coumarin 545 at 546 nm.³ To change the spectral and, therefore, the laser action properties of a pyrromethene-BF₂ complex (4,4-difluoro-4-bora-3a,4a-diaza-s-indacene), we performed substitutions in the 2-, 6-, and 8-positions of the pyrromethene-BF₂ molecule while maintaining the four methyl groups in the 1-, 3-, 5-, and 7-positions.


For testing, the same small dye laser was used as in Ref. 4. Its highest input energy was 10 J from an EG&G FX139C-2 flashlamp, producing a pulse ~600 ns long at the halfwidth and having an ~200-ns rise time. The laser output energy was measured with a Scientech model 365 power/energy meter. The spectroscopic equipment used to measure the triplet extinction coefficients ϵ_T of the new laser dyes was the same as in Ref. 5. McClure's method was used.⁶ The fluorescence spectra and quantum fluorescence yields Q_F were measured with a Perkin-Elmer Corp. LS-5B luminescence spectrometer. The visible/UV absorption spectra of the dyes were recorded with a Cary 17 spectrophotometer.

The synthesis of the four substituted pyrromethene-BF₂ complexes 3-6 will be reported elsewhere. Rhodamine 575

Table I. Quantum Fluorescence Yield Q_F , Fluorescence Intensity Maximum λ_F , Absorption (*S-S*) Intensity Maximum λ_S (*S-S*) Absorption (Extinction) Coefficient ϵ_S , and Laser Action Wavelength λ_{LAS} of the Pyrromethene Complexes 3-6

Complex	Q_F	λ_F (nm)	λ_S (nm)	$\log \epsilon_S$	λ_{LAS} (nm)
3	0.70	544	518	4.83	566
4	0.83	547	518	4.86	567
5	0.35	530	493	5.00	556
6	0.31	533	494	4.62	559

was purchased from Exciton and rhodamine 110 (rhodamine 560) from Eastman Kodak Co. Methanol (99.9% spectroscopic grade) was obtained from Aldrich Chemical Co., ethyl alcohol (190 proof punctilious) from Quantum Chemical Corp., USI Division, and 2-methyltetrahydrofuran from Lancaster Synthesis, Ltd.

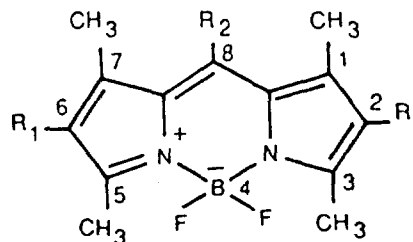

(1) $R_1 = R_2 = H$ (TMP-BF₂); (2) $R_1 = H, R_2 = CH_3$ (PMP-BF₂); (3) $R_1 = R_2 = CH_3$ (HMP-BF₂); (4) $R_1 = C_2H_5, R_2 = CH_3$; (5) $R_1 = CO_2C_2H_5, R_2 = C_2H_5$; (6) $R_1 = NO_2, R_2 = CH_3$.

1,2,3,5,6,7,8-heptamethylpyrromethene-BF₂ complex 1 (HMP-BF₂) showed laser action BB at ~566 nm when dissolved in a 2×10^{-4} -M solution of ethyl alcohol. Laser action wavelength (BB) and other spectroscopic data are collected in Table I; 2×10^{-4} M was about the upper limit of solubility in methyl or ethyl alcohol of the new laser dyes we studied. When methyl alcohol was used as a solvent, HMP-BF₂ lased only 2/3 as efficiently as in ethyl alcohol.

Because rhodamine 560 exhibits laser action BB at ~570 nm (in a 2×10^{-4} -M solution in ethyl alcohol), it was used for comparison. Note, however, that rhodamine 560 cannot be labeled as an efficient or very stable xanthene laser dye. We, therefore, also used rhodamine 575 (in a 2×10^{-4} -M solution in ethyl alcohol) as a standard. It showed laser action BB at 579 nm. This dye can be grouped among the better xanthene laser dyes in efficiency and photostability.

As is apparent from Fig. 1, HMP-BF₂ lases about twice as efficiently as rhodamine 560 and ~10% more efficiently than

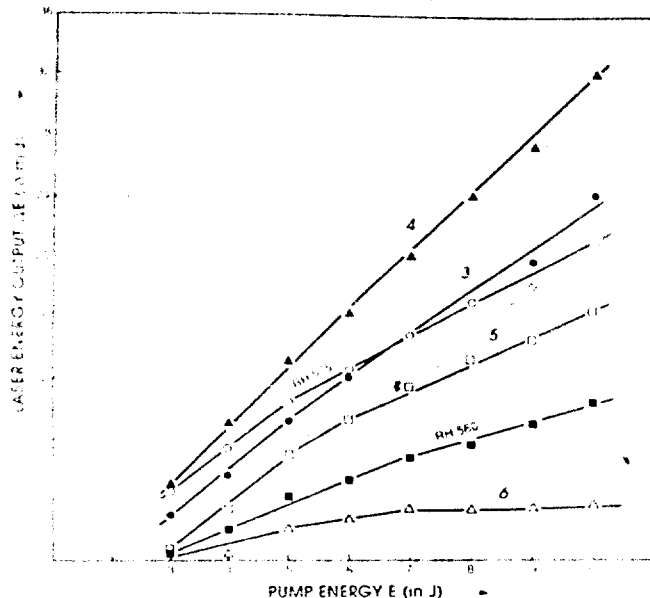


Fig. 1. Laser energy output ΔE (mjoules) as a function of flashlamp pump energy E (joules) of 2×10^{-4} M solutions of rhodamine 560 (RH 560), rhodamine 575 (RH 575), and the complexes 3 and 4 dissolved in ethyl and 5 and 6 in methyl alcohol.

rhodamine 575. HMP- BF_2 and rhodamine 575 showed comparable photostability.

1,3,5,7,8-pentamethyl-2,6-diethylpyrromethene- BF_2 complex 4 exhibited efficient laser action in a 2×10^{-4} -M solution in ethyl alcohol. In methyl alcohol, it lased with about 2/3 the efficiency shown in the ethyl alcohol solution. From the experimental results shown in Fig. 1, complex 4 lased ~ 3 times more efficiently than rhodamine 560 and $\sim 50\%$ more efficiently than rhodamine 575. Compared with rhodamine 6G,³ it lases $\sim 10\%$ more efficiently.³ Complex 4 and rhodamine 575 showed about the same photostability.

To obtain the ϵ_T values, we used the 514.5-nm line from an ion-argon cw laser for excitation. Noteworthy is the exceptionally low ϵ_T value of complex 4 over the fluorescence (laser action) spectral region. This ϵ_T (567) = 1.5×10^3 -liter/mole cm value was similar to that obtained for PMP- BF_2 (reported in Ref. 3) and appears to be the key factor in the remarkable laser action properties of the pyrromethene- BF_2 laser dyes. We have ϵ_T (570) = 7.9×10^3 liter/mole cm for rhodamine 560 (Ref. 7) and ϵ_T (580) = 6.6×10^3 liter/mole cm for rhodamine 575.⁸ It is probable that complex 4 lases with a higher efficiency than HMP- BF_2 because of its higher Q_F value.

1,3,5,7-tetramethyl-8-ethyl-2,6-dicarbethoxy-pyrromethene- BF_2 complex 5. This dye lased with considerably less efficiency than dyes 3 and 4, which is not surprising considering its low Q_F value. Nevertheless, this new dye lases with higher efficiency than rhodamine 560 (Fig. 1). The data in this figure were obtained from a 2×10^{-4} -M solution in methyl alcohol, where the dye lased $\sim 10\%$ more efficiently than observed from a solution in ethyl alcohol.

1,3,5,7,8-pentamethyl-2,6-dinitropyrrromethene- BF_2 complex 6. This compound is an oddity among laser dyes,

because it exhibits laser action under flashlamp excitation—although not very efficiently. It is well known that aromatic nitrocompounds rarely show fluorescence; however, in a few cases weak fluorescence has been noted. Heretofore, nitrocompounds were not known to show laser action under flashlamp excitation. Complex 6 was routinely prepared in investigating P- BF_2 chemistry. Because it showed some fluorescence ($Q_F = 0.31$), we tested its ability to lase. Photochemically, the compound was unstable. Therefore, the values for Q_F and λ_{lase} shown in Table I are not too accurate.

In summary, of the four new dyes we tested, complex 4 easily surpassed rhodamine 560 in efficiency and rivals rhodamine 6G as one of the most efficient of the laser dyes. Other 2,6,8-position trisubstituted pyrromethene- BF_2 complexes should either lase in different spectral regions or possess different laser/physical properties, e.g., efficiency, solubility (water), and photostability. Employing these new laser dyes should result in improved performance (increased average power output) in dye lasers.

Over the last few years, it has been stated that dye lasers do not have much of a future compared with the exceptional performance of the newly developed solid state devices like Ti:sapphire and diode lasers. This may be the case for small dye lasers. However, when tunability, high average power operation, and visible laser light output at low cost are required, a large flashlamp pumped dye laser operating with improved laser dyes should be difficult to beat.

The authors gratefully acknowledge the support provided by the Office of Naval Research. One of the authors (T.G.P.) wishes to thank the NOSC Independent Research program for support; another author (J.H.B.) thanks the Board of Regents, Louisiana Education Quality Support Fund, for support under contract LEQSF(86-87)-RD-B-06.

References

1. P. P. Sorokin, J. R. Lankard, E. C. Hammond, and V. L. Maruzzi, "Laser Pumped Stimulated Emissions from Organic Dyes: Experimental Studies and Analytical Comparisons," *IBM J. Res. Dev.* **11**, 130-148 (1967).
2. T. G. Pavlopoulos, M. Shah, and J. H. Boyer, "Laser Action from a Tetramethylpyrromethene- BF_2 Complex," *Appl. Opt.* **27**, 4998-4999 (1988).
3. T. G. Pavlopoulos, M. Shah, and J. H. Boyer, "Efficient Laser Action from 1,3,5,7,8-Pentamethylpyrromethene- BF_2 Complex and its 2,6-Disulfonate Derivative," *Opt. Commun.* **70**, 425-427 (1989).
4. E. J. Schimitschek, J. A. Trias, P. R. Hammond, R. A. Henry, and R. L. Atkins, "New Laser Dyes with Blue-Green Emission," *Opt. Commun.* **16**, 313-316 (1975).
5. T. G. Pavlopoulos, "Measurement of Triplet Extinction Coefficients of Organic Molecules by McClure's Method," *Spectrochim. Acta A* **43**, 1201-1208 (1987).
6. D. J. McClure, "Excited Triplet States of Some Polyatomic Molecules," *J. Chem. Phys.* **19**, 670-675 (1951).
7. T. G. Pavlopoulos and D. J. Golich, "Triplet Extinction Coefficients of Some Laser Dyes I," *J. Appl. Phys.* **64**, 521-527 (1988).
8. T. G. Pavlopoulos and D. J. Golich, "Triplet Extinction Coefficients of Some Laser Dyes II," *J. Appl. Phys.* **67**, 1203-1206 (1990).