

AD-A248 101



## DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

1a. REPORT SECURITY CLASSIFICATION Unclassified		1b. RESTRICTIVE MARKINGS	
2a. SECURITY CLASSIFICATION AUTHORITY		3. DISTRIBUTION/AVAILABILITY OF REPORT Approval for public release; Distribution unlimited	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE			
4. PERFORMING ORGANIZATION REPORT NUMBER(S) Technical Report No. DU/DC/TR-27		5. MONITORING ORGANIZATION REPORT NUMBER(S)	
6a. NAME OF PERFORMING ORGANIZATION Department of Chemistry Duke University	6b. OFFICE SYMBOL (If applicable)	7a. NAME OF MONITORING ORGANIZATION Office of Naval Research	
6c. ADDRESS (City, State, and ZIP Code) Durham, NC 27706		7b. ADDRESS (City, State, and ZIP Code) 300 North Quincy Street Arlington, VA 22217-5000	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Office of Naval Research	8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER N00014-89-J1545 R&T Code 4135008	
8c. ADDRESS (City, State, and ZIP Code) 800 North Quincy Street Arlington, VA 22217-5000		10. SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO. NR	PROJECT NO. 053
		TASK NO. 841	WORK UNIT ACCESSION NO.
11. TITLE (Include Security Classification) REACTION OF $\text{LiE}(\text{SiMe}_3)_2$ WITH COMPOUNDS CONTAINING FOUR-MEMBERED CORES OF THE GENERAL FORMULA $\text{MEMCl}$ ( $\text{M} = \text{In}, \text{E} = \text{As}, \text{P}; \text{M} = \text{Ga}, \text{E} = \text{As}$ ): NOVEL REARRANGEMENT REACTIONS TO FORM THE ADDUCTS $\text{R}_3\text{M} \cdot \text{As}(\text{SiMe}_3)_3$ ( $\text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{In}; \text{R} = \text{Ph}, \text{M} = \text{Ga}$ )			
12. PERSONAL AUTHOR(S) R. L. Wells, A. T. McPhail, L. J. Jones III, M. F. Self, and R. J. Butcher			
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM _____ TO _____	14. DATE OF REPORT (Year, Month, Day) 1992-03-25	15. PAGE COUNT 21
16. SUPPLEMENTARY NOTATION Accepted for Publication in <u>Organometallics</u>			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	
19. ABSTRACT (Continue on reverse if necessary and identify by block number)  See attached			
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a. NAME OF RESPONSIBLE INDIVIDUAL Richard L. Wells		22b. TELEPHONE (Include Area Code) (919)660-1541	22c. OFFICE SYMBOL

92-07986



00 000 027

[19. ABSTRACT]

REACTION OF  $\text{LiE}(\text{SiMe}_3)_2$  WITH COMPOUNDS CONTAINING FOUR-MEMBERED CORES OF THE GENERAL FORMULA  $\overline{\text{MEMCl}}$  ( $\text{M} = \text{In}, \text{E} = \text{As}, \text{P}; \text{M} = \text{Ga}, \text{E} = \text{As}$ ): NOVEL REARRANGEMENT REACTIONS TO FORM THE ADDUCTS  $\text{R}_3\text{M} \cdot \text{As}(\text{SiMe}_3)_3$  ( $\text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{In}; \text{R} = \text{Ph}, \text{M} = \text{Ga}$ )

RICHARD L. WELLS,\* ANDREW T. McPHAIL, LEONIDAS J. JONES III, and MARK F. SELF

Department of Chemistry, Paul M. Gross Chemical Laboratory, Duke University, Durham, NC 27706, U.S.A.

and

RAY J. BUTCHER

Department of Chemistry, Howard University, Washington D.C. 20059, U.S.A.

*Summary:* The 1:1 reactions of  $\text{R}_2\overline{\text{ME}(\text{SiMe}_3)_2\text{M}(\text{R})_2\text{Cl}}$  with  $\text{LiE}(\text{SiMe}_3)_2$  ( $\text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{In}, \text{E} = \text{P}; \text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{In}, \text{E} = \text{As}; \text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{Ga}, \text{E} = \text{As}; \text{R} = \text{Ph}, \text{M} = \text{Ga}, \text{E} = \text{As}$ ) result in the formation of species containing  $\overline{\text{MEME}}$  core structures as verified by comparison of  $^{13}\text{C}$  and  $^1\text{H}$  NMR spectra, and melting points, to those obtained for authentic samples prepared previously. When reactions were carried out involving  $\text{R}_2\overline{\text{ME}(\text{SiMe}_3)_2\text{M}(\text{R})_2\text{Cl}}$  and  $\text{LiE}'(\text{SiMe}_3)_2$  ( $\text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{In}, \text{E} = \text{P}, \text{E}' = \text{As}; \text{R} = \text{Ph}, \text{M} = \text{Ga}, \text{E} = \text{As}, \text{E}' = \text{P}$ ) novel rearrangements resulted to form  $\text{R}_3\text{M} \cdot \text{As}(\text{SiMe}_3)_3$  [ $\text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{In}$  (1) or  $\text{R} = \text{Ph}, \text{M} = \text{Ga}$  (2)], respectively. Both 1 and 2 are formed *via* the homoleptic redistribution of the substituents on both the metal center and the pnictide. Compound 1 belongs to the rhombohedral system, space group  $\text{R}\bar{3}$  with cell constants:  $a = 16.185(5)$ ,  $c = 12.265(4) \text{ \AA}$ ,  $V = 2782(2) \text{ \AA}^3$ ,  $Z = 3$ . Compound 2 crystallizes in the monoclinic system, space group  $\text{P}2_1/\text{c}$  with cell constants:  $a = 18.867(5)$ ,  $b = 19.307(2)$ ,  $c = 20.926(6) \text{ \AA}$ ,  $\beta = 123.27(1)^\circ$ ,  $V = 6373(5) \text{ \AA}^3$ ,  $Z = 8$ .

OFFICE OF NAVAL RESEARCH

Grant NO0014-89-J-1545

R&T Code 4135008

Technical Report No. DU/DC/TR-27

REACTION OF  $\text{LiE}(\text{SiMe}_3)_2$  WITH COMPOUNDS CONTAINING FOUR-MEMBERED CORES  
OF THE GENERAL FORMULA  $\text{MEMCl}$  ( $\text{M} = \text{In}, \text{E} = \text{As}, \text{P}; \text{M} = \text{Ga}, \text{E} = \text{As}$ ):  
NOVEL REARRANGEMENT REACTIONS TO FORM THE ADDUCTS  
 $\text{R}_3\text{M} \cdot \text{As}(\text{SiMe}_3)_3$  ( $\text{R} = \text{Me}_3\text{SiCH}_2, \text{M} = \text{In}; \text{R} = \text{Ph}, \text{M} = \text{Ga}$ )

by

R. L. Wells, A. T. McPhail, L. J. Jones III, M. F. Self,

and

R. J. Butcher

Prepared for Publication in  
*Organometallics*

Duke University  
Department of Chemistry  
Durham, NC 27706

March 24, 1992



Accession For	
EX-100	<input checked="" type="checkbox"/>
EX-101	<input type="checkbox"/>
EX-102	<input type="checkbox"/>
Classification	
By	
Distribution	
Availability Codes	
Avail and/or	Special
Dist	

A-1

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

(Submitted to *Organometallics* December 8, 1991)  
(Revised version returned March 11, 1992)

**REACTION OF  $\text{LiE}(\text{SiMe}_3)_2$  WITH COMPOUNDS CONTAINING FOUR-MEMBERED CORES OF THE GENERAL FORMULA  $\overline{\text{MEMCl}}$  ( $\text{M} = \text{In}$ ,  $\text{E} = \text{As}$ ,  $\text{P}$ ;  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}$ ): NOVEL REARRANGEMENT REACTIONS TO FORM THE ADDUCTS  $\text{R}_3\text{M} \cdot \text{As}(\text{SiMe}_3)_3$  ( $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ;  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$ )**

**RICHARD L. WELLS,\* ANDREW T. McPHAIL, LEONIDAS J. JONES III, and MARK F. SELF**

Department of Chemistry, Paul M. Gross Chemical Laboratory, Duke University, Durham, NC 27706, U.S.A.

and

**RAY J. BUTCHER**

Department of Chemistry, Howard University, Washington D.C. 20059, U.S.A.

(Received ..... , 1991)

**Summary:** The 1:1 reactions of  $\text{R}_2\overline{\text{ME}(\text{SiMe}_3)_2\text{M}(\text{R})_2\text{Cl}}$  with  $\text{LiE}(\text{SiMe}_3)_2$  ( $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ,  $\text{E} = \text{P}$ ;  $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ,  $\text{E} = \text{As}$ ;  $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}$ ;  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}$ ) result in the formation of species containing  $\overline{\text{MEME}}$  core structures as verified by comparison of  $^{13}\text{C}$  and  $^1\text{H}$  NMR spectra, and melting points, to those obtained for authentic samples prepared previously. When reactions were carried out involving  $\text{R}_2\overline{\text{ME}(\text{SiMe}_3)_2\text{M}(\text{R})_2\text{Cl}}$  and  $\text{LiE}'(\text{SiMe}_3)_2$  ( $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ,  $\text{E} = \text{P}$ ,  $\text{E}' = \text{As}$ ;  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}$ ,  $\text{E}' = \text{P}$ ) novel rearrangements resulted to form  $\text{R}_3\text{M} \cdot \text{As}(\text{SiMe}_3)_3$  [ $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$  (**1**) or  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$  (**2**)], respectively. Both **1** and **2** are formed *via* the homoleptic redistribution of the substituents on both the metal center and the pnictide. Compound **1** belongs to the rhombohedral system, space group  $\text{R}\bar{3}$  with cell constants:  $a = 16.185(5)$ ,  $c = 12.265(4)$  Å,  $V = 2782(2)$  Å<sup>3</sup>,  $Z = 3$ . Compound **2** crystallizes in the monoclinic system, space group  $\text{P}2_1/\text{c}$  with cell constants:  $a = 18.867(5)$ ,  $b = 19.307(2)$ ,  $c = 20.926(6)$  Å,  $\beta = 123.27(1)^\circ$ ,  $V = 6373(5)$  Å<sup>3</sup>,  $Z = 8$ .

The last decade has seen considerable attention focused on the formation of suitable precursors to III-V compound semiconductors.<sup>1-6</sup> As a part our research in this area, we recently reported the isolation of "mixed-bridge" compounds of the heavier group III elements (*i.e.*, four-membered ring systems of the type  $\overline{\text{MEMCl}}$  where  $\bar{\text{M}} = \text{In}$ ,  $\text{E} = \text{P}^7$  or  $\text{As}$ ,<sup>8</sup> and  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}^{9-12}$ ), whose chlorine atom should allow introduction of other functional groups within these systems. From these precursors, the isolation of mixed III-V compound semiconductors may be possible. Herein we report the reactions of several mixed-bridge compounds with  $\text{LiAs}(\text{SiMe}_3)_2$  and  $\text{LiP}(\text{SiMe}_3)_2$  to produce dimeric compounds and on the reactions of  $(\text{Me}_3\text{SiCH}_2)_2\overline{\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}}$ ,<sup>7</sup> and  $\text{Ph}_2\overline{\text{GaAs}(\text{SiMe}_3)_2\text{Ga}(\text{Ph})_2\text{Cl}}$ <sup>10</sup> with  $\text{LiAs}(\text{SiMe}_3)_2$  and  $\text{LiP}(\text{SiMe}_3)_2$ , respectively, to give the arsine adducts  $(\text{Me}_3\text{SiCH}_2)_3\text{In}\cdot\text{As}(\text{SiMe}_3)_3$  (1) and  $\text{Ph}_3\text{Ga}\cdot\text{As}(\text{SiMe}_3)_3$  (2). Both 1 and 2 can be prepared by direct 1:1 reaction of  $\text{R}_3\text{M}$  ( $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ;  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$ ) with  $\text{As}(\text{SiMe}_3)_3$ .

## EXPERIMENTAL

**General Considerations.** All manipulations were performed using general Schlenk, dry box, or high vacuum techniques. Solvents (including those for NMR spectra) were appropriately dried and distilled under argon prior to use. Literature methods were used to prepare  $\text{R}_2\overline{\text{ME}(\text{SiMe}_3)_2\text{M}(\text{R})_2\text{Cl}}$  ( $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ,  $\text{E} = \text{P}$ ;<sup>7</sup>  $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ,  $\text{E} = \text{As}$ ;<sup>8</sup>  $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}$ ;<sup>11</sup>  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}$ ),<sup>10</sup>  $\text{LiAs}(\text{SiMe}_3)_2$ , and  $\text{LiP}(\text{SiMe}_3)_2$ .<sup>13</sup>  $^1\text{H}$  and  $^{13}\text{C}\{^1\text{H}\}$  NMR spectra were obtained on a Varian XL-300 at 300.0 and 75.4 MHz, respectively, and referenced to TMS via the residual protons or carbons of the solvent. Melting points (uncorrected) were taken in sealed capillaries. Elemental analyses were performed by E+R Microanalytical Laboratory, Inc., Corona, New York.

**Synthesis of  $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$ ,<sup>7</sup>  $[(\text{Me}_3\text{SiCH}_2)_2\text{In}\cdot\text{As}(\text{SiMe}_3)_2]_2$ ,<sup>8</sup>  $[(\text{Me}_3\text{SiCH}_2)_2\text{GaAs}(\text{SiMe}_3)_2]_2$ ,<sup>11</sup> and  $[\text{Ph}_2\text{GaAs}(\text{SiMe}_3)_2]_2$ .<sup>10</sup>** All

reactions were carried out similarly as follows: 0.01 mmol of the mixed bridge species was placed in a 5 mm NMR tube in the dry box. Next, 0.01 mmol of the appropriate lithium salt was added (eq. 1). The tube was immersed into liquid dinitrogen and to it approximately 1 mL of benzene- $d_6$  was vacuum distilled. The reaction mixture was maintained at  $-196^\circ\text{C}$  and the NMR tube flame sealed. The mixture was allowed to thaw to room temperature and the progress of the reaction monitored at 10 minute intervals via  $^1\text{H}$  NMR spectroscopy until no resonances corresponding to the starting materials were evident, usually after 40 min. Upon completion of the reaction, the  $^{13}\text{C}$  NMR spectrum was obtained (for  $[(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2]_2$ , a  $^{31}\text{P}$  NMR spectrum was also recorded), the tube was returned to the dry box, the material recovered, and a melting point taken for comparison to an authentic sample of the respective dimer.

**Synthesis of  $(\text{Me}_3\text{SiCH}_2)_3\text{In} \cdot \text{As}(\text{SiMe}_3)_3$  (1) from  $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  and  $\text{LiAs}(\text{SiMe}_3)_2$ .** In the dry box,  $(\text{Me}_3\text{SiCH}_2)_2\text{InP}(\text{SiMe}_3)_2\text{In}(\text{CH}_2\text{SiMe}_3)_2\text{Cl}$  (0.587 g, 0.741 mmol) was dissolved in 50 mL of toluene in a 100-mL one-necked round-bottomed flask equipped with a Teflon valve and a micro-stirbar.  $\text{LiAs}(\text{SiMe}_3)_2$  (0.180 g, 0.771 mmol) in 15 mL of hexane and 5 mL of tetrahydrofuran was slowly added drop-wise. Initially the reaction mixture was clear. However, after the solution was sealed and stirred at room temperature for 3 days it became quite orange.  $\text{LiCl}$  was filtered off, and the volatiles were removed *in vacuo* to yield a thick sticky orange oil. Addition of approximately 10 mL of warm hexane to this oil, followed by cooling to  $-15^\circ\text{C}$  for 30 minutes, afforded an intractable orange oil and, based on As, a quantitative yield of pale yellow crystals of **1** (0.156 g, slightly contaminated by the oily residue) suitable for X-ray analysis, m.p.  $210 - 223^\circ\text{C}$  (dec to brown liquid). Anal. Calcd (Found) for  $\text{C}_{21}\text{H}_{60}\text{AsInSi}_6$ : C, 37.60 (37.27); H, 9.01 (9.18); As, 3.91 (3.70).  $^1\text{H}$  NMR:  $\delta$  -0.06 (s, 6 H,  $\text{CH}_2$ ), 0.30 (s, 27 H,  $\text{SiMe}_3$ ), 0.31 (s, 27 H,  $\text{AsSiMe}_3$ ).  $^{13}\text{C}$  { $^1\text{H}$ } NMR:  $\delta$  3.21 (s,  $\text{SiMe}_3$ ), 4.00 (s,  $\text{AsSiMe}_3$ ), 6.18 (s,  $\text{CH}_2$ ).

**Synthesis of  $\text{Ph}_3\text{Ga} \cdot \text{As}(\text{SiMe}_3)_3$  (2) from  $\text{Ph}_2\text{GaAs}(\text{SiMe}_3)_2\text{Ga}(\text{Ph})_2\text{Cl}$  and  $\text{LiP}(\text{SiMe}_3)_2$ .** Using the above procedure,  $\text{Ph}_2\text{GaAs}(\text{SiMe}_3)_2\text{Ga}(\text{Ph})_2\text{Cl}$  (0.100g, 0.142 mmol) dissolved in 20 mL of benzene was allowed to react with  $\text{LiP}(\text{SiMe}_3)_2$  (0.032 g, 0.142 mmol) in 8 mL of benzene and 0.5 mL of THF to give a pale yellow solution.  $\text{LiCl}$  was filtered off and the volatiles were removed *in vacuo*. Dissolving the off-white thick tacky residue in 4 mL of warm toluene followed by cooling to  $-15^\circ\text{C}$  afforded colorless crystals of 2, from an intractable oil, suitable for X-ray analysis in 29.2% yield (0.035g, based on As), m.p.  $173 - 185^\circ\text{C}$ . Anal. Calcd (Found) for  $\text{C}_{27}\text{H}_{42}\text{AsGaSi}_3$ : C, 54.46 (54.36); H, 7.11 (7.14).  $^1\text{H}$  NMR:  $\delta$  0.13 (s, 27 H,  $\text{SiMe}_3$ ), 7.29 (m, 3 H, Ph), 7.38 (m, 6 H, Ph), 8.10 (m, 6 H, Ph).  $^{13}\text{C}$   $\{^1\text{H}\}$  NMR:  $\delta$  3.22 (s,  $\text{SiMe}_3$ ), 127.81 (partially obscured by solvent, s, Ph), 138.99 (bs, Ph).

**Direct synthesis of 1 and 2 .** Compounds 1 and 2 can be prepared by the 1:1 reaction of the trialkylmetal with  $\text{As}(\text{SiMe}_3)_3$ .  $\text{R}_3\text{M}$  ( $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ;  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$ ) (0.250 mmol) was dissolved in 15 mL of toluene and  $\text{As}(\text{SiMe}_3)_3$  (0.250 mmol) in 15 mL of toluene was added slowly drop-wise. The clear solution was stirred at room temperature for 12 h. Then, the volatiles were removed *in vacuo* to yield the adduct quantitatively as colorless crystals.

**X-ray Crystallography.** Single crystals of 1 and 2 were mounted in 0.6 mm thin walled-glass capillaries under an inert atmosphere of argon and flame sealed. Relevant crystallographic data are given in Table I. For 1, data were collected on a Siemens R3m/V diffractometer (Laboratory for the Structure of Matter, Naval Research Laboratory, Washington, D. C.). Cell constants and an orientation matrix for data collection corresponded to a rhombohedral cell. The space group was determined by a combination of extinctions and the successful solution and refinement of the structure. Intensity data were corrected for the usual Lorentz and polarization effects. An empirical absorption correction was applied and equivalent reflections were averaged [ $R_{\text{merge}} = 0.050$  on ( $I$ )] to yield 1838 reflections out of which 1549 with  $F > 3\sigma(F)$  were retained. The structure was solved by direct methods and refined to convergence using SHELXTL PLUS <sup>14</sup> . Non-hydrogen atoms were refined using anisotropic thermal

parameters; hydrogen atoms, in calculated positions, were included in structure factor calculations. The weighting scheme was based on counting statistics and included a factor ( $p = 0.0140$ ) to downweight the intense reflections. The final difference map contained maxima and minima of 1.80 and  $-2.61 \text{ e}/\text{\AA}^3$ , respectively, located in close proximity to the In atom. Final fractional atomic coordinates are given in Table II. Selected bond distances and angles are given in Table IV. A thermal ellipsoid diagram showing the atom labeling scheme for the unique part of **1** is presented in Figure 1.



For **2**, oscillation and Weissenberg photographs provided preliminary unit cell parameters and space group information. The space group was established unequivocally from the Laue symmetry and systematic absences ( $0k0$  when  $k$  is odd,  $h0l$  when  $l$  is odd). Reflections  $hkl$  were systematically weak when  $h + l$  was odd, indicating that Ga and As atoms were related by an approximate  $B$  lattice centering. Intensity data, recorded on an Enraf-Nonius CAD-4 diffractometer (Crystal Structure Center, Duke University), were corrected for the usual Lorentz and polarization effects. An empirical absorption correction was applied, and equivalent reflections were averaged [ $R_{\text{merge}} = 0.026$  on ( $I$ )] to yield 13098 reflections out of which those 8565 with  $I > 3\sigma(I)$  were retained for the analysis. The crystal structure was solved by the heavy-atom approach. The asymmetric unit contains two crystallographically independent molecules of **2**. Approximate coordinates for the Ga and As atoms were derived from a Patterson map. The remaining non-hydrogen atoms were located in a series of difference and weighted  $F_o$  Fourier syntheses, and their distributions distinguished the Ga and As atoms. Several rounds of full-matrix least-squares adjustment of nonhydrogen atom positional and thermal parameters (at first isotropic, then anisotropic) followed. Hydrogen atoms were incorporated at their calculated positions and an extinction correction was included as a variable in the later iterations which converged. A final difference Fourier synthesis revealed no unusual features (max. 1.4; min.  $-2.6 \text{ e}/\text{\AA}^3$ , located ca.  $0.2 - 0.5 \text{ \AA}$  from the Ga and As atoms). Crystallographic calculations were performed using the Enraf-Nonius Structure Determination Package (SDP).<sup>15</sup> For all structure factor calculations, neutral atom scattering factors and their anomalous dispersion corrections were



taken from ref. 16. Fractional atomic coordinates are listed in Table III. Selected distances and angles are given in Table V. A thermal ellipsoid diagram showing the atom labeling scheme and solid-state conformation of one of the molecules in the asymmetric crystal unit of **2** is presented in Figure 2.

## RESULTS AND DISCUSSION

Currently, our laboratory is investigating the potential use of mixed-bridge type compounds for the synthesis of further III-V oligomeric units. As part of an earlier study, it was shown by us that the reaction of  $(\text{Me}_3\text{CCH}_2)_2\text{GaAs}(\text{SiMe}_3)_2\text{Ga}(\text{CH}_2\text{CMe}_3)_2\text{Cl}$  with  $\text{LiAs}(\text{SiMe}_3)_2$  yields  $[(\text{Me}_3\text{CCH}_2)_2\text{GaAs}(\text{SiMe}_3)_2]_2^{12}$ , and we decided to explore whether this reactivity could be generally applied to similar mixed-bridge systems. The following transformations were accomplished according to equation 1.



These facile and clean reactions result in the formation of dimeric systems where the bridging chlorine has been replaced by the pnictide of the lithium salt.

Similarly, the introduction of two different pnictide atoms into these systems to give rings of the formula  $\overline{\text{MEME}}'$  ( $\text{E} = \text{As}$  and  $\text{E}' = \text{P}$ ) was investigated. Interestingly, when  $\text{R}_2\overline{\text{ME}(\text{SiMe}_3)_2\text{M}(\text{R})_2}\text{Cl}$  and  $\text{LiE}'(\text{SiMe}_3)_2$  ( $\text{R} = \text{Me}_3\text{SiCH}_2$ ,  $\text{M} = \text{In}$ ,  $\text{E} = \text{P}$ ,  $\text{E}' = \text{As}$ ;  $\text{R} = \text{Ph}$ ,  $\text{M} = \text{Ga}$ ,  $\text{E} = \text{As}$ ,  $\text{E}' = \text{P}$ ) are allowed to react, rearrangements occur to form  $(\text{Me}_3\text{SiCH}_2)_3\text{In}\cdot\text{As}(\text{SiMe}_3)_3$  (**1**) and  $\text{Ph}_3\text{Ga}\cdot\text{As}(\text{SiMe}_3)_3$  (**2**). No indium-phosphorus or gallium-phosphorus compounds were isolated. Reagent purity was verified through spectroscopic (NMR) and physical (mp) measurements prior to, and after, use and no contamination was detected.

Though the precise pathway of these transformations is not known, the fact that substituent transfer occurred at both the metal and the arsenic centers in each is quite remarkable. The subtle combination of both an arsenic and phosphorus atom in these systems substantially changes their reaction pathways. These reactions are apparently much more complicated than was originally envisioned.

A literature review reveals no structural reports of indium-arsenic adducts. Compound **1** has a three-fold axis of symmetry coincidental with the indium arsenic bond. The As-In-C and C-In-C angles are  $101.2(4)^\circ$  and  $116.3(3)^\circ$ , respectively. Undoubtedly, the large C-In-C angle is indicative of steric repulsions from the  $\text{Me}_3\text{SiCH}_2$  groups. The In-As-Si and Si-As-Si bond angles are  $112.9(1)^\circ$  and  $105.8(1)^\circ$ , respectively. The large In-As-Si angle is interesting and may be due to electronic repulsions between the arsenic atom and  $\text{SiMe}_3$  groups or repulsions between the  $\text{SiMe}_3$  groups and neighboring  $\text{Me}_3\text{SiCH}_2$  groups. In sharp contrast to either  $\text{As}(\text{SiMe}_3)_3$  or  $(\text{Me}_3\text{SiCH}_2)_3\text{In}$ , **1** is quite stable and will not undergo appreciable decomposition even upon exposure to air for over 10 h or undergo further reaction (*via*  $^1\text{H}$  NMR spectroscopy and melting point) when heated in chlorobenzene at  $140^\circ\text{C}$  for 3 days in a sealed pressure tube.

There have been three structural reports of gallium-arsenic adducts, *viz.*  $\text{Cl}_3\text{Ga}\cdot\text{AsMe}_3$  (**4**) (only the unit cell parameters were given)<sup>17</sup>  $(\text{Me}_3\text{CCH}_2)_2(\text{Cl})\text{Ga}\cdot\text{As}(\text{SiMe}_3)_3$  (**5**),<sup>12</sup> and  $(\text{C}_6\text{F}_5)_3\text{Ga}\cdot\text{As}(\text{SiMe}_3)_3$  (**6**).<sup>18</sup> Compounds **6** and **2** crystallize in the monoclinic space group  $P2_1/c$ , and although they are isostructural, they are not isomorphous. In **6**, one molecule occupies each of the four general positions of the space group while the asymmetric unit of **2** consists of two structurally identical, but crystallographically independent, molecules that lie in general positions. Values for mean bond angles in **2** and **6** [Ga-As-Si =  $113.0^\circ$ , Si-As-Si =  $105.8^\circ$ , As-Ga-C =  $104.7^\circ$ , C-Ga-C =  $113.8^\circ$ , smallest Si-As-Ga-C torsion angle =  $24.7^\circ$  in **2**; Ga-As-Si =  $113.2^\circ$ , Si-As-Si =  $105.5^\circ$ , As-Ga-C =  $106.8^\circ$ , C-Ga-C =  $112.0^\circ$ , smallest Si-As-Ga-C torsion angle =  $17.1^\circ$  in **6**] are very alike. The mean Ga-As bond length of  $2.567\text{ \AA}$  in **2** is slightly longer than that of  $2.550(4)\text{ \AA}$  in **6** but both are significantly shorter than the value of  $2.626(1)\text{ \AA}$  in **5**. The mean Ga-C(ar) bond distance in **2** ( $2.01\text{ \AA}$ ) is the same as in **6** ( $2.012\text{ \AA}$ ) whereas the mean

As-Si bond lengths in **2** at 2.320 Å is significantly shorter than the corresponding value of 2.403 Å in **6**, reflecting differences in non-bonded intramolecular steric interactions ( $H...H < F...H$ ) between substituents on the Ga and As centers. As with **1**, compound **2** is similarly unreactive under refluxing conditions.

**Acknowledgment.** This work was financially supported by the Office of Naval Research. RJB acknowledges the American Society for Engineering Education for a 1991 Summer Senior Faculty Fellowship. The assistance of Cliff George at the Naval Research Laboratory is appreciated.

**Supplementary Material Available:** Tables of hydrogen atom coordinates and isotropic thermal parameters, anisotropic temperature factors, complete lists of bond distances and angles, including torsion angles for **1** and **2** (16 pages); a listing of observed and calculated structure amplitudes for **1** and **2** (64 pages). Ordering information is given on any current masthead page.

## References

- (1) Cowley, A. H.; Jones, R. A. *Angew. Chem. Intl. Ed. Engl.* **1989**, 28, 1208.
- (2) Byrne, E. K.; Douglas, T.; Theopold, K. H. *Mat. Res. Symp. Proc.* **1989**, 131, 59.
- (3) Olshavsky, M. A.; Goldstein, A. N.; Alivisatos, A. P. *J. Am. Chem. Soc.* **1990**, 112, 9438.
- (4) Douglas, T.; Theopold, K. H. *Inorg. Chem.* **1991**, 30, 596.
- (5) Glass, A. M. *Science* **1987**, 235, 1003.
- (6) Wells, R. L. *Coord. Chem. Rev.* **1992**, 112, 273.
- (7) Wells, R. L.; McPhail, A. T.; Self, M. F. *Organometallics*, **1992**, 11, 221.
- (8) Wells, R. L.; Jones, L. J.; McPhail, A. T.; Alvanipour, A. *Organometallics*, **1991**, 10, 2345.
- (9) Wells, R. L.; Holley, W. K.; Shafieezad, S.; McPhail, A. T.; Pitt, C. G. *Phosphorus, Sulfur, Silicon and Relat. Elem.* **1989**, 41, 15.
- (10) Holley, W. K.; Wells, R. L.; Shafieezad, S.; McPhail, A. T.; Pitt, C. G. *J. Organomet. Chem.* **1990**, 381, 15.
- (11) Wells, R. L.; Pasterczyk, J. W.; McPhail, A. T.; Johansen, J. D.; Alvanipour, A. *J. Organomet. Chem.* **1991**, 407, 17.
- (12) Wells, R. L.; McPhail, A. T.; Pasterczyk, J. W.; Alvanipour, A. *Organometallics* **1992**, 11, 226.
- (13) Becker, G.; Gutekunst, G.; Wessely, H. J. *Z. Anorg. Allg. Chem.* **1980**, 462, 113.
- (14) Sheldrick, G. M. SHELXTL PLUS, Crystallographic Computing System, Revision 3.42; Nicolet Instrument Corporation: Madison, WI, **1986**.
- (15) Enraf-Nonius Structure Determination Package (SDP 3.0), Enraf-Nonius, Delft, The Netherlands, **1985**.
- (16) *International Tables for X-ray Crystallography*; The Kynoch Press, Birmingham, England, 1974, Vol IV.
- (17) Carter, J. C.; Jugie, G.; Enjalbert, R.; Galy, J. *Inorg. Chem.* **1978**, 17, 1248.
- (18) Wells, R. L.; McPhail, A. T.; Hallock, R. B.; Johansen, J. D. *J. Organomet. Chem.* **1991**, submitted.

Captions to Figures

Figure 1. A thermal ellipsoid diagram (40% probability ellipsoids) showing the solid state conformation and atom numbering scheme for the unique fraction of  $(\text{Me}_3\text{SiCH}_2)_3\text{In}\cdot\text{As}(\text{SiMe}_3)_3$  (1); hydrogen atoms have been omitted for clarity.

Figure 2. A thermal ellipsoid diagram (40% probability ellipsoids) showing the solid state conformation of one of the molecules in the asymmetric crystal unit and atom numbering scheme of  $\text{Ph}_3\text{Ga}\cdot\text{As}(\text{SiMe}_3)_3$  (2); hydrogen atoms have been omitted for clarity.

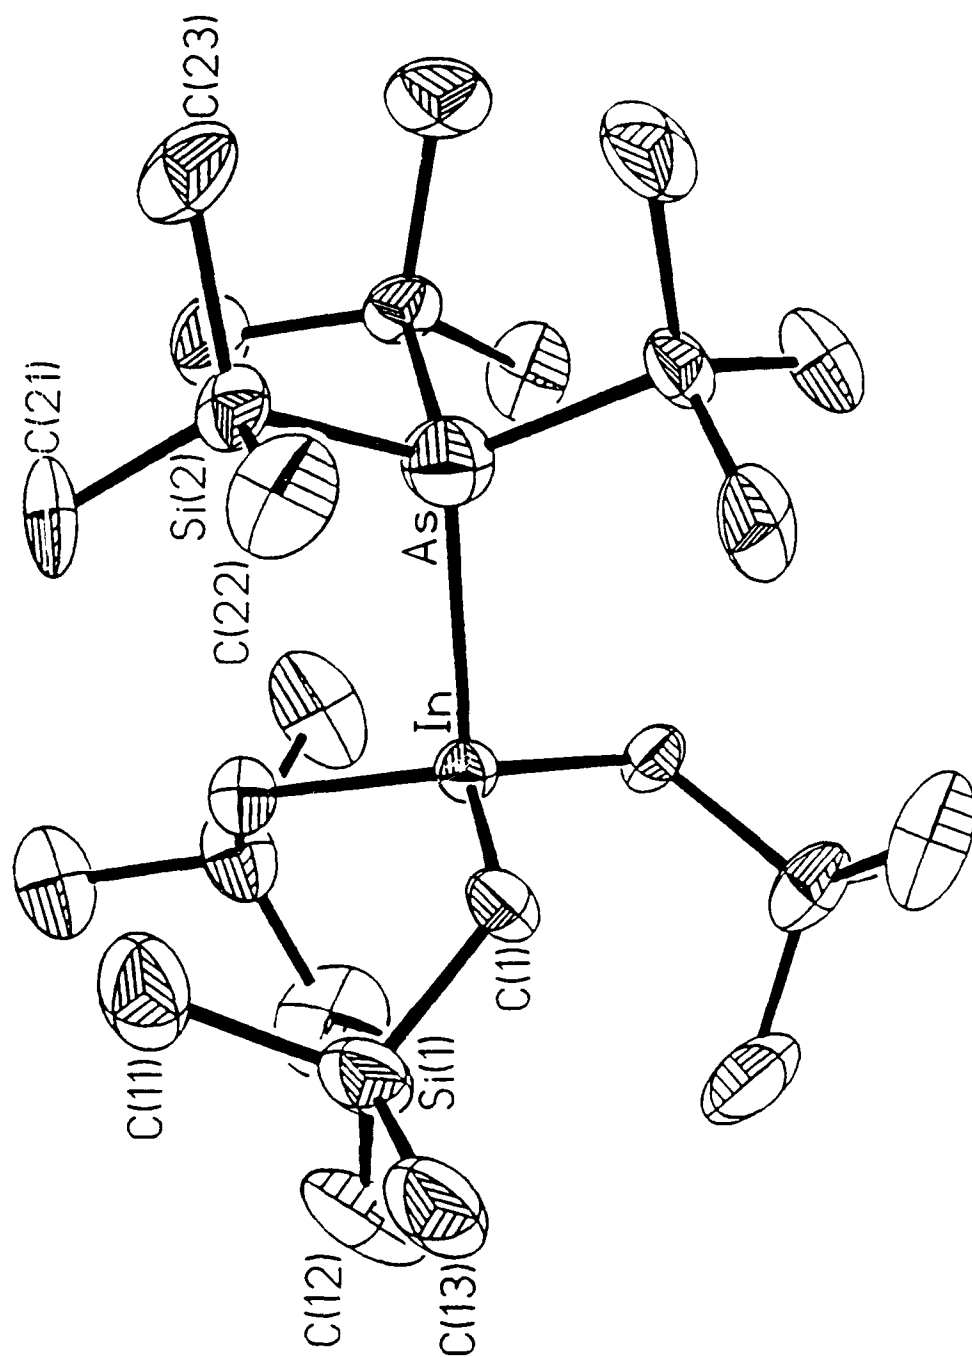


Figure 1

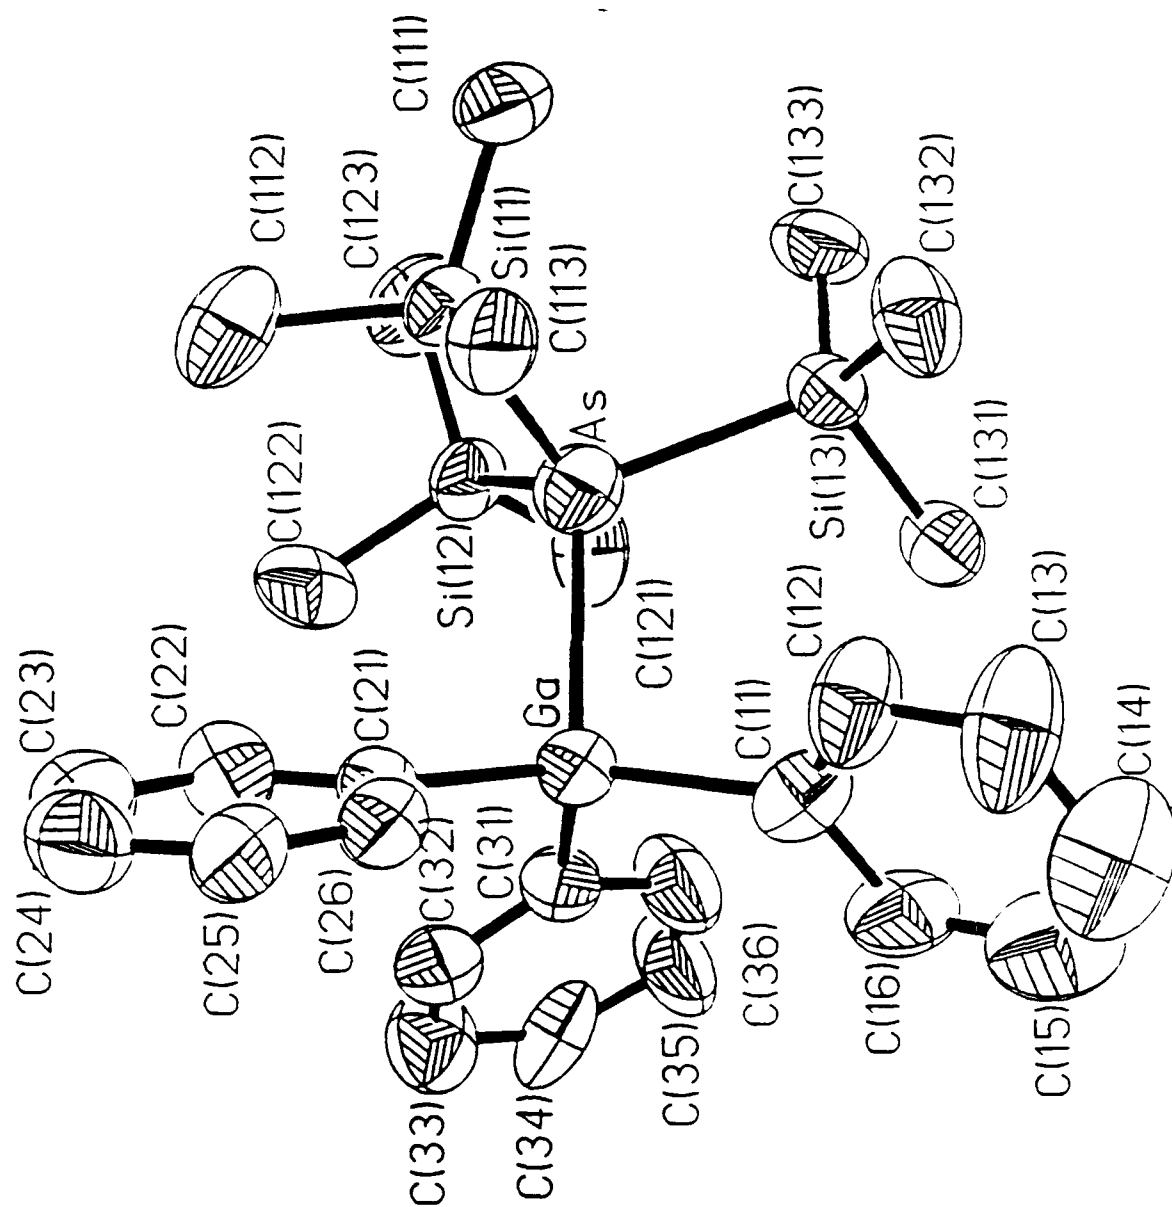


Figure 2

**Table I. Crystallographic Data and Measurements for  
(Me<sub>3</sub>SiCH<sub>2</sub>)<sub>3</sub>In·As(SiMe<sub>3</sub>)<sub>3</sub> (1) and Ph<sub>3</sub>Ga·As(SiMe<sub>3</sub>)<sub>3</sub> (2)**

	1	2
molecular formula	C <sub>21</sub> H <sub>60</sub> AsInSi <sub>6</sub>	C <sub>27</sub> H <sub>42</sub> AsGaSi <sub>3</sub>
formula weight	671.0	595.54
crystal system	rhombohedral	monoclinic
space group	R3	P2 <sub>1</sub> /c
<i>a</i> , Å	16.185(5)	18.867(5)
<i>b</i> , Å	16.185(5)	19.307(2)
<i>c</i> , Å	12.265(4)	20.926(6)
$\alpha$ , deg	90.00	90.00
$\beta$ , deg	90.00	123.27(1)
$\gamma$ , deg	120.00	90.00
no. of orient. refls; $\theta$ , deg, range	25; 13-17	25; 36-40
<i>V</i> , Å <sup>3</sup>	2782(2)	6373(5)
<i>Z</i>	3	8
<i>D</i> <sub>calcd.</sub> g cm <sup>-3</sup>	1.201	1.241
temp, °C	-49	25
crystal dimensions, mm	0.42 x 0.66 x 0.54	0.30 x 0.30 x 0.75
<i>T</i> <sub>max</sub> : <i>T</i> <sub>min</sub>	0.863:0.655	1.00:0.86
radiation (wavelength)	Mo- <i>K</i> α (0.71073 Å)	Cu- <i>K</i> α (1.5418 Å)
$\mu$ , cm <sup>-1</sup>	17.09	35.2
scan type	$\omega$ -2 $\theta$	$\omega$ -2 $\theta$



Table I. (continued)

scan width, deg	$1.0 + \Delta_{a1, a2}$	$1.00 + 0.14 \tan \theta$
$\theta_{\max}$ , deg	22.5	75
intensity control reflns	$\bar{9} 0 0, 0 9 0, 0 0 9$	$4 3 \bar{1} 2, 12 \bar{3} \bar{4}, 12 \bar{3} 4$
variation; repeat time	<1%; every 97 refl.	<2%; every 2h
no of rflns recorded	1838 (-h,+k, $\pm$ l)	13499 (+h,+k, $\pm$ l)
no of rflns retained, $I > 3\sigma(I)$	1549	8565
no of parameters refined	88	578
extinction correction	$6.6(5) \times 10^{-7}$	$2.9(3) \times 10^{-7}$
R, $R_w^a$	0.067, 0.097	0.090, 0.144
goodness-of-fit <sup>b</sup>	0.78	3.0
max shift; esd in final least-squares cycle	0.02	0.03

---

<sup>a</sup>  $R = \Sigma ||F_o| - |F_c|| / \Sigma |F_o|$ ;  $R_w = [\Sigma w (|F_o| - |F_c|)^2 / \Sigma w |F_o|^2]^{1/2}$ ;  $\Sigma w \Delta^2 [w = 1/\sigma^2(|F_o|)$ ,  $\Delta = (|F_o| - |F_c|)]$  was minimized.

<sup>b</sup> Goodness-of-fit =  $[\Sigma w \Delta^2 / (N_{\text{observations}} - N_{\text{parameters}})]^{1/2}$ .

**Table II. Non-hydrogen Atom Fractional Coordinates and Equivalent Isotropic Thermal Parameters for 1, with Estimated Standard Deviations in Parentheses.**

atom	<i>x</i>	<i>y</i>	<i>z</i>	<i>U</i> (eq)
In	0	0	0.2554	0.040(1)
As	0	0	0.282(3)	0.080(1)
Si(1)	0.1386(3)	0.2218(3)	0.3794(4)	0.073(2)
Si(2)	0.0110(3)	0.1360(2)	-0.0447(3)	0.055(2)
C(1)	0.1343(9)	0.1294(9)	0.2899(11)	0.050(3)
C(11)	0.0763(17)	0.2781(14)	0.3060(22)	0.114(12)
C(12)	0.0869(20)	0.1740(19)	0.5137(20)	0.123(15)
C(13)	0.2630(13)	0.3194(13)	0.4070(18)	0.094(9)
C(21)	-0.0747(12)	0.1602(11)	0.0301(18)	0.079(8)
C(22)	0.1303(12)	0.2354(11)	-0.0209(16)	0.085(8)
C(23)	-0.0197(18)	0.1195(14)	-0.1981(14)	0.090(11)

**Table III. Non-hydrogen Atom Fractional Coordinates and Equivalent Isotropic Thermal Parameters for 2, with Estimated Standard Deviations in Parentheses.**

atom	x	y	z	$B_{eq}(\text{\AA}^2)$
As	0.22363(6)	0.05619(6)	0.46852(5)	4.79(2)
Ga	0.35749(5)	0.06523(5)	0.60435(5)	3.54(2)
Si(11)	0.1614(1)	-0.0531(1)	0.4365(1)	3.83(5)
Si(12)	0.2540(1)	0.0840(2)	0.3777(1)	4.37(5)
Si(13)	0.1156(1)	0.1310(1)	0.4453(1)	4.05(5)
C(11)	0.3128(6)	0.1047(5)	0.6665(5)	4.7(2)
C(12)	0.2519(6)	0.0729(6)	0.6710(5)	6.3(2)
C(13)	0.2262(7)	0.0981(8)	0.7166(6)	8.7(3)
C(14)	0.2642(8)	0.1572(8)	0.7600(6)	9.1(3)
C(15)	0.3232(7)	0.1913(7)	0.7542(6)	7.8(3)
C(16)	0.3485(6)	0.1658(6)	0.7071(6)	5.8(3)
C(21)	0.4025(5)	-0.0314(5)	0.6307(5)	4.1(2)
C(22)	0.4353(6)	-0.0659(5)	0.5947(6)	5.3(2)
C(23)	0.4714(6)	-0.1307(6)	0.6184(7)	6.3(3)
C(24)	0.4750(8)	-0.1634(6)	0.6760(8)	7.4(4)
C(25)	0.4400(8)	-0.1324(7)	0.7133(7)	7.1(4)
C(26)	0.4048(6)	-0.0680(6)	0.6895(6)	5.6(3)
C(31)	0.4333(5)	0.1300(5)	0.5958(5)	4.3(2)
C(32)	0.5085(5)	0.1103(6)	0.6073(5)	5.1(2)
C(33)	0.5643(7)	0.1543(7)	0.6052(6)	7.1(3)
C(34)	0.5396(8)	0.2263(7)	0.5891(8)	9.8(4)
C(35)	0.4676(7)	0.2468(6)	0.5805(8)	7.8(4)
C(36)	0.4138(6)	0.2002(6)	0.5788(7)	6.5(3)
C(111)	0.0492(6)	-0.0503(6)	0.3522(6)	5.6(3)
C(112)	0.2236(8)	-0.1117(6)	0.4132(6)	7.0(3)
C(113)	0.1642(6)	-0.0871(6)	0.5218(5)	5.1(2)
C(121)	0.2654(7)	0.1784(7)	0.3730(6)	7.5(3)
C(122)	0.3538(5)	0.0413(7)	0.4059(5)	6.1(3)

Table III (continued)

atom	x	y	z	$B_{eq}(\text{\AA}^2)$
C(123)	0.1747(8)	0.0554(8)	0.2815(6)	7.5(4)
C(131)	0.1654(5)	0.2137(5)	0.4941(5)	5.0(2)
C(132)	0.0582(6)	0.0942(6)	0.4846(6)	6.4(3)
C(133)	0.0414(6)	0.1477(6)	0.3425(6)	6.0(3)
As'	0.27163(7)	-0.05857(7)	0.03520(6)	5.39(3)
Ga'	0.13900(5)	-0.07283(5)	-0.09992(5)	3.42(2)
Si(11')	0.2656(1)	0.0347(1)	0.1018(1)	4.12(5)
Si(12')	0.3908(1)	-0.0414(2)	0.0321(1)	5.50(6)
Si(13')	0.2994(2)	-0.1538(2)	0.1129(2)	4.97(7)
C(11')	0.0663(4)	-0.1416(5)	-0.0911(4)	3.8(2)
C(12')	0.0405(5)	-0.1366(5)	-0.0411(5)	4.8(2)
C(13')	-0.0126(7)	-0.1817(7)	-0.0385(6)	6.9(3)
C(14')	-0.0457(7)	-0.2381(6)	-0.0904(6)	7.2(3)
C(15')	-0.0180(7)	-0.2466(6)	-0.1395(6)	6.4(3)
C(16')	0.0331(5)	-0.1978(5)	-0.1409(5)	4.8(2)
C(21')	0.0891(4)	0.0217(5)	-0.1278(4)	3.5(2)
C(22')	0.1241(6)	0.0785(6)	-0.1406(5)	5.0(3)
C(23')	0.0850(7)	0.1426(6)	-0.1634(6)	6.4(3)
C(24')	0.0088(7)	0.1542(5)	-0.1726(6)	6.3(3)
C(25')	-0.0224(6)	0.1015(6)	-0.1562(6)	6.3(3)
C(26')	0.0142(5)	0.0351(5)	-0.1340(5)	4.3(2)
C(31')	0.1816(5)	-0.1105(5)	-0.1628(4)	4.1(2)
C(32')	0.1765(6)	-0.0709(5)	-0.2208(5)	5.7(2)
C(33')	0.2050(8)	-0.0985(8)	-0.2650(6)	8.5(3)
C(34')	0.2210(8)	-0.1639(8)	-0.2637(6)	8.9(3)
C(35')	0.2255(7)	-0.2051(7)	-0.2076(6)	7.4(3)
C(36')	0.2063(6)	-0.1786(6)	-0.1576(5)	5.5(2)
C(111')	0.3418(7)	0.0292(6)	0.2060(5)	5.8(3)
C(112')	0.2899(10)	0.1181(6)	0.0693(7)	9.0(4)
C(113')	0.1580(6)	0.0345(7)	0.0844(5)	6.9(3)
C(121')	0.4164(6)	-0.1249(9)	0.0077(7)	8.7(4)

Table III (continued)

atom	<i>x</i>	<i>y</i>	<i>z</i>	<i>B</i> <sub>eq</sub> (Å <sup>2</sup> )
C(122')	0.3654(6)	0.0203(8)	-0.0419(6)	7.6(3)
C(123')	0.4797(6)	-0.0048(8)	0.1248(7)	7.5(3)
C(131')	0.2712(10)	-0.2327(6)	0.0530(7)	9.2(5)
C(132')	0.2338(7)	-0.1472(7)	0.1565(6)	7.0(3)
C(133')	0.4181(8)	-0.1570(7)	0.1932(7)	7.5(4)

**Table IV. Selected Bond Distances (Å) and Angles (deg) for 1, with Estimated Standard Deviations in Parentheses.**

Bond Lengths			
In-As	2.778(4)	In-C(1)	2.177(10)
As-Si(2)	2.298(5)		
Bond Angles <sup>a</sup>			
As-In-C(1)	101.2(3)	C(1)-In-C(1)a	116.3(6)
In-As-Si(2)	112.9(1)	Si(2)-As-Si(2)a	105.8(2)
Torsion Angle <sup>b</sup>			
Si(2)-As-In-C(1)	57.7(4)		

<sup>a</sup> Numbered atoms denoted with a lettered postscript are symmetry equivalents to similarly numbered non-postscripted atoms by the transformation (-y, x - y, z) or (y - x, -x, z).

<sup>b</sup> The torsion angle A-B-C-D is defined as positive if, when viewed along the B-C bond, atom A must be rotated clockwise to eclipse atom D.

**Table V. Selected Bond Distances (Å) and Angles (°) for 2, with Estimated Standard Deviations in Parentheses.**

	Bond Lengths	
	Unprimed Molecule	Primed Molecule
As-Ga	2.571(1)	2.563(1)
As-Si(11)	2.327(3)	2.318(3)
As-Si(12)	2.329(3)	2.308(3)
As-Si(13)	2.321(3)	2.316(3)
Ga-C(11)	2.05(1)	1.99(1)
Ga-C(21)	2.00(1)	1.99(1)
Ga-C(31)	1.98(1)	2.02(1)
Bond Angles		
Ga-As-Si(11)	114.45(7)	113.98(7)
Ga-As-Si(12)	110.74(7)	111.15(8)
Ga-As-Si(13)	113.98(7)	113.41(8)
Si(11)-As-Si(12)	106.6(2)	106.0(2)
Si(11)-As-Si(13)	104.9(1)	105.1(2)
Si(12)-As-Si(13)	105.5(1)	106.6(1)
As-Ga-C(11)	103.3(2)	106.0(2)
As-Ga-C(21)	104.6(2)	104.1(1)
As-Ga-C(31)	105.3(2)	105.1(2)
C(11)-Ga-C(21)	115.7(4)	113.6(4)
C(11)-Ga-C(31)	113.1(4)	111.2(4)
C(21)-Ga-C(31)	113.3(4)	115.7(4)

Table V (continued)

	Torsion Angles <sup>a</sup>	
	Unprimed Molecule	Primed Molecule
Si(11)-As-Ga-C(21)	24.6(3)	24.4(3)
Si(12)-As-Ga-C(31)	23.8(3)	26.8(3)
Si(13)-As-Ga-C(11)	23.9(3)	24.6(3)

---

<sup>a</sup>The torsion angle A-B-C-D is defined as positive if, when viewed along the B-C bond, atom A must be rotated clockwise to eclipse atom D.



TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)  
Chemistry Division, Code 1113  
800 North Quincy Street  
Arlington, VA 22217-5000

Dr. James S. Murday (1)  
Chemistry Division, Code 6100  
Naval Research Laboratory  
Washington, DC 20375-5000

Dr. Robert Green, Director (1)  
Chemistry Division, Code 385  
Naval Weapons Center  
China Lake, CA 93555-6001

Dr. Eugene C. Fischer (1)  
Code 2840  
David Taylor Research Center  
Annapolis, MD 21402-5067

Dr. Elek Lindner (1)  
Naval Ocean Systems Center  
Code 52  
San Diego, CA 92152-5000

Commanding Officer (1)  
Naval Weapons Support Center  
Dr. Bernard E. Douda  
Crane, IN 47522-5050

Dr. Richard W. Drisko (1)  
Naval Civil Engineering Lab.  
Code L52  
Port Hueneme, CA 93043

Dr. Harold H. Singerman (1)  
David Taylor Research Center  
Code 283  
Annapolis, MD 21402-5067

Chief of Naval Research (1)  
Special Assistant for Marine  
Corps Matters  
Code 00MC  
800 North Quincy Street  
Arlington, VA 22217-5000

Defense Technical  
Information Center (2)  
Building 5, Cameron Station  
Alexandria, VA 22314