

AD-A248 700



CONTINUATION PAGE

Form Approved
OMB No. 0704-0188

Estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, reviewing the collection of information, Send comments regarding this burden estimate or any other aspect of this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503

1. REPORT DATE April 8, 1992		3. REPORT TYPE AND DATES COVERED Technical Report #14	
4. TITLE AND SUBTITLE Synthesis of Side Chain Liquid Crystal Polymers by Living Ring Opening Metathesis Polymerization. 2. Influence of Molecular Weight, Polydispersity and...		5. FUNDING NUMBERS C N00014-89-J1542	
6. AUTHOR(S) Zen Komiya, Coleen Pugh, Richard R. Schrock			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Massachusetts Institute of Technology Department of Chemistry, 6-331 77 Massachusetts Avenue Cambridge, MA 02139		8. PERFORMING ORGANIZATION REPORT NUMBER N00014-89-J1542	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Department of the Navy Office of Naval Research 800 North Quincy Street Arlington, VA 22217-5000		10. SPONSORING/MONITORING AGENCY REPORT NUMBER 4132038	
11. SUPPLEMENTARY NOTES Macromolecules, submitted.			
12a. DISTRIBUTION AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.		12b. DISTRIBUTION CODE DTIC SELECTE APR 20 1992 S D D	
13. ABSTRACT (Maximum 200 words) The living ring opening metathesis polymerization of 5-carbo(n-[(4'-methoxy-4-biphenyl)oxy]alkyl)bicyclo[2.2.1]hept-2-ene (1-n, n=9-12) with Mo(CH-t-Bu)(NAr)(O-t-Bu) ₂ (Ar=2,6-C ₆ H ₃ -i-Pr ₂) is described. Polymers with degrees of polymerization from 5 to 100 and narrow molecular weight distributions (M _w /M _n =1.07-1.28) were obtained in high yield. All polymers exhibit side chain crystallization along with a nematic mesophase. Isotropization temperatures increase with increasing molecular weight and then become independent of molecular weight at approximately 30-50 repeat units. Side chain crystallization is suppressed as molecular weight increases.			
14. SUBJECT TERMS living ring opening metathesis polymerization, side chain liquid crystalline polymers (SCLCPs)		15. NUMBER OF PAGES 26	
		16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT UL

92-09921



OFFICE OF NAVAL RESEARCH

Contract N00014-89-J1542

R&T Code 4132038

Technical Report No. 14

Synthesis of Side Chain Liquid Crystal Polymers by Living Ring Opening Metathesis Polymerization. 2. Influence of Molecular Weight, Polydispersity, and Flexible Spacer Length ($n = 9-12$) on the Thermotropic Behavior of the Resulting Polymers.

by

Zen Komiya, Coleen Pugh[‡], and Richard R. Schrock

Submitted

to

Macromolecules

[‡]Carnegie Mellon University
Department of Chemistry
4400 Fifth Avenue
Pittsburgh, PA 15213

[†]Massachusetts Institute of Technology
Department of Chemistry, 6-331
77 Massachusetts Avenue
Cambridge, MA 02139 USA

Accession For	
NTIS GRA&I J	
DTIC TAB	
Unannounced	
Justification	
By	
Dist. bullet.	
Availability	
Dist	Avail. and/or Spec.
A-1	

March 31, 1992

Reproduction in whole or in part is permitted for any purpose of the United States Government.

This document has been approved for public release and sale; its distribution is unlimited.

Synthesis of Side Chain Liquid Crystal Polymers by Living Ring Opening Metathesis
Polymerization. 2. Influence of Molecular Weight, Polydispersity, and Flexible Spacer Length
($n = 9-12$) on the Thermotropic Behavior of the Resulting Polymers

by

Zen Komiya, Coleen Pugh[†], and Richard R. Schrock*

Contribution from

Department of Chemistry 6-331
Massachusetts Institute of Technology
Cambridge, Massachusetts 02139

Abstract

The living ring opening metathesis polymerization of 5-carbo{n-[(4'-methoxy-4-biphenyl)oxy]alkyl}bicyclo[2.2.1]hept-2-ene (**1-n**, $n = 9-12$) with $\text{Mo}(\text{CH-}i\text{-Bu})(\text{NAr})(\text{O-}i\text{-Bu})_2$ ($\text{Ar} = 2,6\text{-C}_6\text{H}_3\text{-}i\text{-Pr}_2$) is described. Polymers with degrees of polymerization from 5 to 100 and narrow molecular weight distributions ($M_w/M_n = 1.07-1.28$) were obtained in high yield. All polymers exhibit side chain crystallization along with a nematic mesophase. Isotropization temperatures increase with increasing molecular weight and then become independent of molecular weight at approximately 30-50 repeat units. Side chain crystallization is suppressed as molecular weight increases.

* To whom correspondence should be addressed.

[†] Present address: Department of Chemistry, Carnegie Mellon University, 4400 Fifth Ave., Pittsburgh, PA 15213.

INTRODUCTION

Side chain liquid crystalline polymers (SCLCP)s have been prepared mainly by radical polymerization of (meth)acrylates and by the hydrosilation of polymethyl siloxane backbones with mesogenic olefins. Although extensive data has accumulated on the structure/property relations of SCLCPs using these two synthetic routes, much of it is contradictory.¹ These findings demonstrated the need for more comprehensive and systematic studies of SCLCP's prepared using living polymerization methods.^{2,3,4,5,6} Ideally, motions of mesogenic side chains should be completely decoupled from those of the polymeric main chain. Although the motions of the main chain and side chains are only partially decoupled by a spacer, decoupling becomes more effective with increasing spacer length.¹ However, most SCLCPs containing long spacers undergo side chain crystallization. Side chain crystallization is depressed by polymerization of monomers which undergo conformational isomerism,^{7,8,9} and by copolymerization of constitutionally isomeric monomers;^{10,11} decoupling is enhanced by phase separation of the main chain from the mesogenic side chains.^{12,13,14,15}

A relatively recent method of preparing living polymers consists of ring opening metathesis polymerization (ROMP) of strained cyclic olefins^{16,17} by initiators whose activity has been "tuned" in order to limit secondary metathesis of the double bonds in the polymer chain. The most readily available suitable cyclic olefins are norbornene and substituted norbornadiene derivatives. ROMP initiators with perhaps the greatest potential are molybdenum complexes of the type $\text{Mo}(\text{CHR})(\text{NAr})(\text{O}-i\text{-Bu})_2$ ¹⁸ ($\text{Ar} = 2,6\text{-C}_6\text{H}_3\text{-}i\text{-Pr}_2$, $\text{R} = i\text{-Bu}$ or CMe_2Ph) since they appear to tolerate a large variety of functional groups on norbornene and norbornadiene monomers.^{19,20} (So far the analogous tungsten derivatives²¹ do not appear to be as tolerant.) The molybdenum catalysts offer an opportunity to prepare new side chain liquid crystalline polymers with a controlled chain length.

In the first paper in this series²² we described the living ROMP of 5-carbo(*n*-[(4'-methoxy-4-biphenyl)oxy]alkyl)bicyclo[2.2.1]hept-2-ene)s (**1-n**) with $n = 2-8$, and discussed the dependence of the thermotropic behavior of poly(**1-n**) on polymer molecular weight,

polydispersity, and the length of the flexible spacer. In contrast to poly(1-n) with $n = 2-8$, polymers with $n = 9-12$ exhibit side chain crystallization in addition to the nematic mesophase. In this paper we describe the synthesis and thermotropic behavior of poly(1-n) with crystallizable side chains as a function of molecular weight and spacer length.

RESULTS AND DISCUSSION

Synthesis of monomers

Monomers 1-n (exo:endo = 1:3) were synthesized as shown in Scheme I by reaction of the appropriate n-bromo-1-alcohol with 4-methoxy-4'-hydroxybiphenyl,²³ followed by esterification of the mesogenic alcohols with an isomeric mixture of 5-norbornene-2-carboxylic acid chloride. All monomers are crystalline and form no mesophase. They exhibit a single melting endotherm on heating and a single crystallization exotherm on cooling, as observed by differential scanning calorimetry (DSC). These findings contrast to analogous findings for monomers 1-n with shorter n-alkoxy substituents, which display crystalline polymorphism. The first and second heating scans are identical, as are all cooling scans.

Polymerization of 1-n

Monomer 1-n was quantitatively polymerized in 1 hour in tetrahydrofuran (THF) at room temperature in a reaction initiated by $\text{Mo}(\text{CH}-i\text{-Bu})(\text{NAr})(\text{O}-i\text{-Bu})_2$. The living polymer was quenched with benzaldehyde to give a benzylidene terminated polymer upon reaction of the living alkylidene with benzaldehyde in a Wittig fashion (Scheme II). The molecular weight of poly(1-n) was controlled by varying the molar ratio of the monomer to Mo initiator ($[\text{M}]/[\text{I}]$). The polymerization is quantitative and the polymers were free of unreacted monomer after a single precipitation.

The results of the polymerizations are summarized in Table I, and the gel permeation chromatograms (GPC's) of poly(1-9) and poly(1-11) are shown in Figure 1. The polydispersities ($\text{PDI} = M_w/M_n$) are lower than 1.20 in most cases, but are as high as 1.28 for some of the higher molecular weight polymers as a result of a small double molecular weight fraction. As shown in Figure 2, a linear relationship is obtained by plotting the number average

molecular weight (M_n) of poly(1-n) as a function of $[M]/[I]$ for ratios up to 100. The linear relationships and low polydispersities are consistent with a living polymerization under the conditions employed.

Proton NMR resonances of poly(1-n) at 5.2-5.6 ppm (olefinic protons) and at 1.6-2.2 and 2.2-3.0 ppm (cyclopentane ring protons) are quite broad as a result of the lack of stereoregularity of the main chain. In contrast, the aromatic resonances are relatively sharp. All spectral data are consistent with the ring-opened structure.

Thermal characterization of polymers

Thermal characterization of poly(1-n) was carried out by a combination of DSC and thermal polarized optical microscopy. All DSC cooling scans and the second and subsequent heating scans were identical when the same rates were used. The complete thermal transitions from the second heating and first cooling scans are summarized in Table I.

DSC traces of the second heating and first cooling scans of poly(1-9) and poly(1-10) are shown in Figures 3 and 4, respectively. Oligomers with less than approximately 50 repeat units exhibit crystalline melting in addition to a nematic-isotropic transition. In these cases, the melting and crystallization transitions overlap the glass transition, which therefore makes T_g difficult to determine accurately. T_g values reported for those polymers which do not crystallize therefore are more reliable than values for the crystallizable oligomers. More reliable T_g values were obtained for the crystallizable polymers by analyzing samples quenched from the isotropic melt using liquid nitrogen. However, even the quenched samples of the lowest molecular weight oligomers and poly(1-11) tend to crystallize during the next heating scan and T_g values of these samples therefore are still less reliable than those for non-crystalline samples.

Oligomers of 1-9 and 1-10 evidently crystallize in two different modifications. This is obvious with poly(1-10), which exhibits two melting endotherms in some cases. As shown in Figure 4, the 10mer of poly(1-10) crystallizes in only the more stable modification if it is annealed at 49°C for 1 hour, and the extent of crystallization increases with annealing ($\Delta H = 5.94$ kJ/mru). Although poly(1-9) exhibits only a single melting endotherm, Figure 3 shows that annealing the

10mer at 50°C for 1 hour also results in a more stable crystalline modification ($T_m = 64^\circ\text{C}$, $\Delta H = 3.54\text{kJ/mru}$). Since side chain crystallization is kinetically controlled and the rate of crystallization decreases as molecular weight increases, crystallization is suppressed as the molecular weight increases and disappears in any polymer that contains more than approximately 50 repeat units. Annealing the 51mer of poly(1-10) at 55°C for 1 hour does induce a slight amount of crystallization ($T_m = 62^\circ\text{C}$; $\Delta H = 0.84\text{ kJ/mru}$; Figure 4).

The thermal behavior of poly(1-11) is almost the same as that of poly(1-10). Oligomers also crystallize in two different modifications (Figure 5), although annealing induces crystallization of only the more stable modification. For example, a 10mer of poly(1-11) which had crystallized on cooling at 44°C showed two melting endotherms, while only a single melting endotherm ascribable to the more stable crystalline form ($T_m = 62^\circ\text{C}$, $\Delta H = 6.53\text{ kJ/mru}$) is observed after the sample was annealed at 46°C for 1 hour. All polymers also exhibit an enantiotropic nematic mesophase.

In the polymer that contains the largest methylene side chain (poly(1-12)) the side chains have the greatest tendency to crystallize. Although the nematic mesophase appears to be enantiotropic for all chain lengths (Figure 6), it actually is monotropic in the two shortest oligomers. The nematic-isotropic transition of the 7 mer is seen as a shoulder on the melting endotherm in the second heating scan shown in Figure 6. However, this sample exhibits a single melting peak at 87°C ($\Delta H = 10.5\text{ kJ/mru}$) on the first heating scan, which is higher than the isotropization temperature. Annealing the 11 mer of poly(1-12) also leads to crystallization of a modification which melts at a temperature exceeding that at which isotropization takes place.

Thermal polarized optical microscopy demonstrates that all of the polymers exhibit textures characteristic of nematic mesophases. A representative threaded marbled nematic texture of poly(1-9) (9 mer), and a representative schlieren nematic texture of poly(1-11) (33mer) are shown in Figure 7. These textures do not change upon cooling the sample, until crystallization takes place. Therefore, although the isotropic-nematic transitions of oligo(1-11) and oligo(1-12) appear to have same fine structure, a phase transition apparently is not involved.

The phase transition temperatures of each polymer obtained upon heating are plotted in Figure 8 as a function of the degree of polymerization determined by GPC. Regardless of the length of the spacer and whether the side chain crystallizes or not, isotropization temperatures become independent of molecular weight at approximately 30-50 repeat units, as found also for the poly(1-n) with shorter spacers ($n = 2-8$).²² These results are comparable to those reported for mesogenic polysiloxanes (DP~12),²⁴ polyvinyl ethers (DP~10-20),^{2,3,4,5,6,24} polyacrylates (DP~12-40)^{25,26} and polymethacrylates (DP~12).²⁷ The melting temperatures depend on chain length as discussed earlier. That is, although T_m increases with increasing molecular weight, the primary effect of increasing molecular weight is to decrease the extent and the rate of side chain crystallization, especially in the most stable modification. Therefore, crystallization and melting are not observed at higher molecular weights for poly(1-9) and poly(1-10). At all chain lengths the side chains in poly(1-11) and poly(1-12) crystallize to some extent, although the extent of side chain crystallization and the change in enthalpy of melting decrease with increasing chain length. Although the enthalpy change of the nematic-isotropic transition is small and somewhat scattered as a function of chain length, it is relatively independent of molecular weight.

CONCLUSIONS

5-Carbo(n -[(4'-methoxy-4-biphenyl)oxy]alkyl)bicyclo[2.2.1]hept-2-enes with $n = 9-12$ were polymerized by ring opening metathesis polymerization in a living manner. This series of SCLCPs with systematically varying molecular weights exhibit monotropic or enantiotropic nematic mesophases in addition to side chain crystallization. Side chain crystallization is highly kinetically controlled and therefore is suppressed by increasing molecular weight, i.e., the change in enthalpy of melting and therefore the extent of crystallinity decreases as chain length increases. Side chains do not crystallize in high molecular weight poly(1-9) and poly(1-10), which also exhibit enantiotropic nematic mesophases. All side chains of poly(1-11) and poly(1-12) crystallize to some extent, although crystallization is suppressed sufficiently at higher molecular weights that the monotropic nematic mesophase of oligo(1-12) becomes enantiotropic. The isotropization temperatures increase with increasing molecular weight up to 30-50 repeat units, and

then become molecular weight independent.

EXPERIMENTAL

Materials and Methods. All polymerizations were performed under a nitrogen atmosphere in a Vacuum Atmospheres drybox. Tetrahydrofuran (THF) used for polymerizations was vacuum transferred from sodium benzophenone ketyl just before use. Ether and THF used for monomer synthesis were distilled from sodium benzophenone ketyl under nitrogen. Dichloromethane used for purification of monomers was distilled from calcium hydride under nitrogen. Pentane was washed with 5% nitric acid in sulfuric acid, stored over calcium chloride, and then distilled from sodium benzophenone ketyl under nitrogen. 4,4'-Dihydroxybiphenyl (97%), 9-bromo-1-nonanol (97%), 10-bromo-1-decanol (90%), 11-bromo-1-undecanol (98%), and 12-bromo-1-dodecanol (99%) were used as received from Aldrich. 2-Norbornene-5-carboxylic acid chloride (exo:endo = 1:3)²⁸ and 4'-methoxy-4-hydroxybiphenyl²⁹ were prepared as described in the literature. All other reagents and solvents were available commercially and used as received.

300 MHz ¹H-NMR spectra were recorded on a Varian XL-300 spectrometer. All spectra were recorded in CDCl₃ with TMS as internal standard. Molecular weight was determined by gel permeation chromatography (GPC) at room temperature using a set of Shodex KF802.5, 803, 804, 805, 800P columns (700, 2×10³, 2×10⁴, 1×10⁵ Å, and a precolumn respectively), a Knauer differential refractometer, and a Spectroflow 757 absorbance detector set at 300 nm on 0.1-0.3 % w/v samples in THF. The GPC columns were calibrated using polystyrene standards (Polymer Laboratories Ltd.) ranging from 1206 to 1.03×10⁶ MW. A Perkin Elmer DSC-7 differential scanning calorimeter was used to determine the thermal transitions which were read as the maxima and minima of the endothermic and exothermic peaks, respectively. All heating and cooling rates were 20°C/min unless noted otherwise. Glass transition temperatures (T_gs) were read as the middle of the change in the heat capacity. All second and subsequent heating scans are identical. A Nikon optical polarized microscope (magnification 160×) equipped with a Mettler FP82 hot stage and a Mettler FP800 central processor was used to observe the thermal transitions and to

analyze the anisotropic textures.

Synthesis of n -[(4'-methoxy-4-biphenyl)oxy]alkyl-1-ol ($n = 9-12$). All compounds were synthesized by the same procedure used for the analogs with a smaller value of n^{22} as illustrated by the following example. 9-Bromo-1-pentanol (4.9 g, 0.022 mol) was added to a solution of 4'-methoxy-4-hydroxybiphenyl (4.0 g, 0.020 mol) and NaOH (0.89 g, 0.022 mol) in a mixture of ethanol (40 ml) and water (5 ml). After stirring at reflux for 24 h, the reaction mixture was poured into water and the precipitated product was filtered and washed with 150 ml of 10% aq NaOH and water. Recrystallization from ethanol yielded 6.11 g (89%) of colorless crystals.

n -[(4'-Methoxy-4-biphenyl)oxy]-1-alkanol. The proton NMR spectra of the n -[(4'-methoxy-4-biphenyl)oxy]-1-alkanols, $n = 9-12$, are identical: δ 1.25 (t, 1H, OH), 1.3-1.7 (m, 2[n-3]H, $-[CH_2]_{n-3}$), 1.83 (q, 2H, $-CH_2CH_2OAr$), 3.65 (q, 2H, $-CH_2OH$), 3.85 (s, 3H, CH_3O -), 4.00 (t, 2H, $-CH_2OAr$), 6.96 (dd, 4 arom. H), 7.46 (dd, 4 arom. H).

Synthesis of 5-carbo{ n -[(4'-methoxy-4-biphenyl)oxy]alkyl}bicyclo[2.2.1]hept-2-enes (1- n , $n = 9-12$). The 1- n monomers were prepared in 70-80% yield as in the following example. A solution of 2-norbornene-5-carboxylic acid chloride (1.71 g, 0.0104 mmol) in THF (5 ml) was added dropwise to a refluxing slurry of 12-[(4'-methoxy-4-biphenyl)oxy]-1-dodecanol (4.0 g, 0.0104 mmol) and triethylamine (1.1 g, 0.0109 mmol) in THF (40 ml). The solution was stirred at reflux for 24 h. The solution was cooled to room temperature and the solvent was removed on a rotary evaporator. The residue was dissolved in chloroform and the solution was washed with aqueous K_2CO_3 and then water, and dried over anhydrous $MgSO_4$. Concentration of the filtered chloroform solution yielded 4.4 g (84%) of 1-12.

Monomers 1-9 and 1-10 were purified by column chromatography using Al_2O_3 as the stationary phase and THF as eluent, followed by at least two recrystallizations in the drybox from ether, ether:pentane or ether:methylenechloride. Following chromatography on Al_2O_3 , 1-11 and 1-12 were purified by precipitation of a THF solution into methanol because they did not recrystallize well. All monomers were recrystallized or reprecipitated until no improvement was

seen in the polydispersity of polymers prepared using 100 eq. of monomer; ^1H NMR δ 1.32 (d), 1.5 (m), 1.6 (d), 1.94 (m), 2.31 (dd), 2.98 (br s), 3.06 (td), 3.12 (br s) and 3.30 (br s), all non-olefinic norbornene protons of both isomers, 5.95 (dd) and 6.21 (dd), endo olefinic protons, 6.15 (m), exo olefinic protons, 1.2-2.0 (m, $2[\text{n}-2]\text{H}$, $-\text{[CH}_2\text{]}_{\text{n}-2}$ -), 3.86 (s, 3H, $-\text{OCH}_3$), 4.07 (t, 2H, $-\text{CH}_2\text{OAr}$), 4.18 (m, 2H, $-\text{CH}_2\text{OOC}-$). The melting points determined by DSC are: 1-9 78°C; 1-10 68°C; 1-11 83°C; 1-12 77°C.

Polymerization procedure. A solution of $\text{Mo}(\text{CH}-t\text{-Bu})(\text{NAr})(\text{O}-t\text{-Bu})_2^{18}$ (0.2 ml, 0.0205 mol/l) in THF was added in one portion to a rapidly stirred solution of monomer (3 ml, 0.137 mol/l, 100 eq) in THF and the reaction mixture was stirred for 1 h. The polymerization was quenched by addition of 20 μl of benzaldehyde. After 30 min, the solution was added dropwise to methanol (~50 ml) and the precipitated polymer was isolated by centrifugation, washed with methanol and dried in vacuo. In all cases, polymer yields were more than 90% and GPC analyses showed no traces of monomer. Further purification of samples by reprecipitation had no effect on their thermotropic behavior. When 20 eq or less of monomer was used, the catalyst concentration was adjusted to 0.205 mol/l: ^1H -NMR δ 1.0 (m, terminal $t\text{-Bu}$), 1.2-2.2 (br), 2.2-3.2 (br), 3.85 (s, $-\text{OCH}_3$), 4.07 (br, $-\text{CH}_2\text{OAr}$), 4.26 (br, $-\text{CH}_2\text{OOC}-$), 5.15-5.55 (br, olefinic H), 6.97 (br d, arom H), 7.51 (br d, arom H).


Acknowledgements. RRS thanks the Office of Naval Research (N00014-89-J1542) and ZK thanks Japan Synthetic Rubber Company for support.

References

- (1) Percec, V.; Pugh, C. in "Side Chain Liquid Crystal Polymers"; C. B. McArdle, Ed.; Chapman and Hall: New York, 1989; pp 30, and references therein.
- (2) Percec, V.; Lee, M. *Polym. Bull.* **1991**, *25*, 123.
- (3) Percec, V.; Lee, M.; Jonsson, H. *J. Polym. Sci., Polym. Chem., Ed.* **1991**, *29*, 327.
- (4) Percec, V.; Lee, M. *Macromolecules* **1991**, *24*, 1017.
- (5) Percec, V.; Lee, M. *J. Macromol. Sci., Chem. Ed.* **1991**, *A28*, 651.

- (6) Percec, V.; Lee, M. *Macromolecules* **1991**, *24*, 2780.
- (7) Hahn, B.; Percec, V. *Macromolecules* **1987**, *20*, 2961.
- (8) Hsu, C. S.; Percec, V. *Makromol. Chem.* **1987**, *188*, 1017.
- (9) Hsu, C. S.; Rodriguez-Parada, J. M.; Percec, V. *J. Polym. Sci., Polym. Chem. Ed.* **1987**, *25*, 2425.
- (10) Percec, V.; Tomazos, D. *Polym. Bull.* **1987**, *18*, 239.
- (11) Percec, V.; Rodriguez-Parada, J. M.; Ericsson, C.; Nava, H. *Polym. Bull.* **1987**, *17*, 353.
- (12) Hsu, C. S.; Percec, V. *Polym. Bull.* **1987**, *18*, 91.
- (13) Hsu, C. S.; Percec, V. *Polym. Bull.* **1987**, *17*, 49.
- (14) Hsu, C. S.; Percec, V. *Makromol. Chem., Rapid Commun.* **1987**, *8*, 331.
- (15) Percec, V.; Hahn, B. *Macromolecules* **1989**, *22*, 1588.
- (16) Grubbs, R. H.; Tumas, W. *Science* **1989**, *243*, 907.
- (17) Schrock, R. R. *Acc. Chem. Res.* **1990**, *23*, 158.
- (18) Schrock, R. R.; Murdzek, J. S.; Bazan, G. C.; Robbins, J.; DiMare, M.; O'Regan, M. J. *Am. Chem. Soc.* **1990**, *112*, 3875.
- (19) Bazan, G. C.; Schrock, R. R.; Cho, H.; Gibson, V. C. *Macromolecules* **1991**, *24*, 4495.
- (20) Bazan, G.; Khosravi, E.; Schrock, R. R.; Feast, W. J.; Gibson, V. C.; O'Regan, M. B.; Thomas, J. K.; Davis, W. M. *J. Am. Chem. Soc.* **1990**, *112*, 8378.
- (21) Schrock, R. R.; DePue, R. T.; Feldman, J.; Yap, K. B.; Yang, D. C.; Davis, W. M.; Park, L. Y.; DiMare, M.; Schofield, M.; Anhaus, J.; Walborsky, E.; Evitt, E.; Krüger, C.; Betz, P. *Organometallics* **1990**, *9*, 2262.
- (22) Komiya, Z.; Pugh, C.; Schrock, R. R. *Macromolecules*, submitted.
- (23) Finkelmann, H.; Happ, M.; Portugal, M.; Ringsdorf, H. *Makromol. Chem.* **1978**, *179*, 2541.
- (24) Stevens, H.; Rehage, H.; Finkelmann, H. *Macromolecules* **1984**, *17*, 851.
- (25) Portugall, M.; Ringsdorf, H.; Zental, R. *Makromol. Chem.* **1982**, *183*, 2311.

- (26) Uchida, S.; Morita, K.; Miyoshi, K.; Hashimoto, K.; Kawasaki, K. *Mol. Cryst. Liq. Cryst.* **1988**, *155*, 189.
- (27) Percec, V.; Tomazos, D.; Pugh, C. *Macromolecules* **1989**, *22*, 3259.
- (28) Jacobine, A. F.; Glaser, D. M.; Nakos, S. T. *ACS Polym. Mat. Sci. Eng.* **1989**, *60*, 211.
- (29) Rodriguez-Parada, J. M.; Percec, V. *J. Polym. Sci., Polym. Chem. Ed.* **1986**, *24*, 1363.

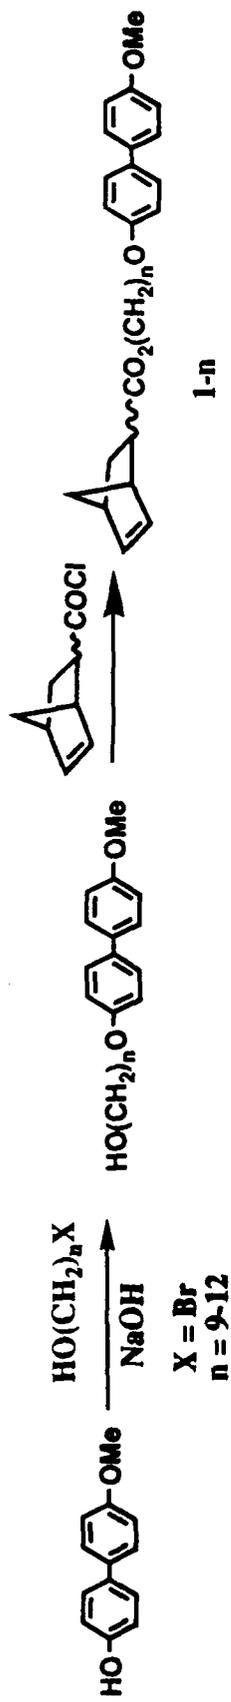

Scheme 1

Table I

Polymerization of 1-n and Characterization of the Resulting Polymers

[1-n]/[Mo]	Theor.	Mn	GPC	PDI	DP	phase transition(°C) and corresponding enthalpy changes (kJ/mru) ^a	
						heating	cooling
1-9	100	46262	47949	1.07	104	g 29 n 91(2.24) i	i 85(2.21) n 22 g
1-9	50	23121	18997	1.08	41	g 25 n 87(1.85) i	i 80(2.16) n 15 g
1-9	20	9252	8649	1.13	19	g 23 k 54(0.66) n 83(1.76) i	i 77(1.54) n 42(0.66) k 19 g
1-9	10	4926	5114	1.14	10	g 21 k 57(-) n 78(4.28) ^b i	i 71(1.54) n 42(0.66) k 17 g
1-9	5	2123	3220	1.17	7	g 18 k 61(-) n 71(6.99) ^b i	i 65(1.28) n 40(2.77) k 32 g
1-10	100	47665	62683	1.26	132	g 23 n 87(1.85) i	i 81(2.04) n 26 g
1-10	50	23833	24378	1.13	51	g 24 n 87(1.98) i	i 79(1.91) n 29 g
1-10	20	9533	8137	1.12	17	g 23 k 55(2.02) n 84(1.76) i	i 76(1.74) n 44(1.70) k 26 g
1-10	10	4767	4710	1.14	10	g 19 k 51(2.37) k 60(0.96) n 78(1.34) i	i 71(1.77) n 41(2.12) k 23 g
1-10	5	2383	3230	1.16	7	g 36 k 60(4.71) n 78(1.35) i	i 67(1.75) n 39(3.52) k 28 g

(Continuation of Table I)

1-11	100	49068	35086	1.23	72	g 40 k 49(1.01) n 84(3.56) i	i 78(3.30) n 45(1.06) k 32 g
1-11	50	24534	16272	1.12	33	g 39 k 52(0.95) n 83(3.07) i	i 77(2.91) n 47(1.25) k 34 g
1-11	20	9814	7226	1.12	15	g 36 k 52(1.90) n 79(2.64) i	i 73(2.35) n 45(2.36) k 31 g
1-11	10	4907	4683	1.15	10	g 25 k 50(1.43) k 55(-1.95) k 63(5.08) n 75(-) ^b i	i 69(2.67) n 44(2.71) k 30 g
1-11	5	2453	3183	1.18	6	g 29 k 62(10.0) n 69(-) ^b i	i 63(2.57) n 44(4.00) k 34 g
1-12	100	50471	49568	1.28	98	g 23 k 61(2.99) n 89(2.70) i	i 83(2.58) n 52(2.16) k 34 g
1-12	50	25236	20830	1.22	41	g 22 k 64(4.83) n 88(2.56) i	i 82(2.38) n 55(2.16) k 38 g
1-12	20	10094	9022	1.13	18	g 38 k 66(2.78) n 85(3.37) i	i 78(3.34) n 58(3.27) k 43 g
1-12	10	5047	5306	1.15	11	g 43 k 63(2.64) n 80(3.01) i	i 74(3.18) n 55(3.23) k 39 g
1-12	5	2524	3421	1.17	7	g 43 k 70(-) n 75(11.70) ^b i	i 68(3.15) n 52(9.28) k 37 g

^a All data except Tgs are from second heating and first cooling scans, and Tgs were determined on heating scans by quenching the samples in liquid nitrogen. ^b Overlapped with previous transition.

Figure Captions

Figure 1. GPC traces of (a) poly(1-9) and (b) poly(1-11). The theoretical and observed (in parentheses) degree of polymerization (DP) are shown on each trace.

Figure 2. Dependence of the number average molecular weight (M_n) and the polydispersity ($PDI = M_w/M_n$) of (a) poly(1-11) and (b) poly(1-12) on the molar ratio of monomer to initiator ($[M]/[I]$).

Figure 3. Normalized DSC thermograms of poly(1-9) observed (a) on the second heating and (b) first cooling scans.

Figure 4. Normalized DSC thermograms of poly(1-10) observed (a) on the second heating and (b) first cooling scans.

Figure 5. Normalized DSC thermograms of poly(1-11) observed (a) on the second heating and (b) first cooling scans.

Figure 6. Normalized DSC thermograms of poly(1-12) observed (a) on the second heating and (b) first cooling scans.

Figure 7. Polarized optical micrographs of the nematic textures observed on cooling (a) poly(1-9) 19mer from the isotropic state; 80°C (magnification 80×) and (b) poly(1-11) 33mer from the isotropic state; 87°C (magnification 160×).

Figure 8. Dependence of the phase transition temperatures on the GPC determined degree of polymerization of (a) poly(1-9), (b) poly(1-10), (c) poly(1-11), and (d) poly(1-12). All of the data are from the second heating scans; \bigcirc k-g, \bigcirc n-k, \bigcirc i-n.

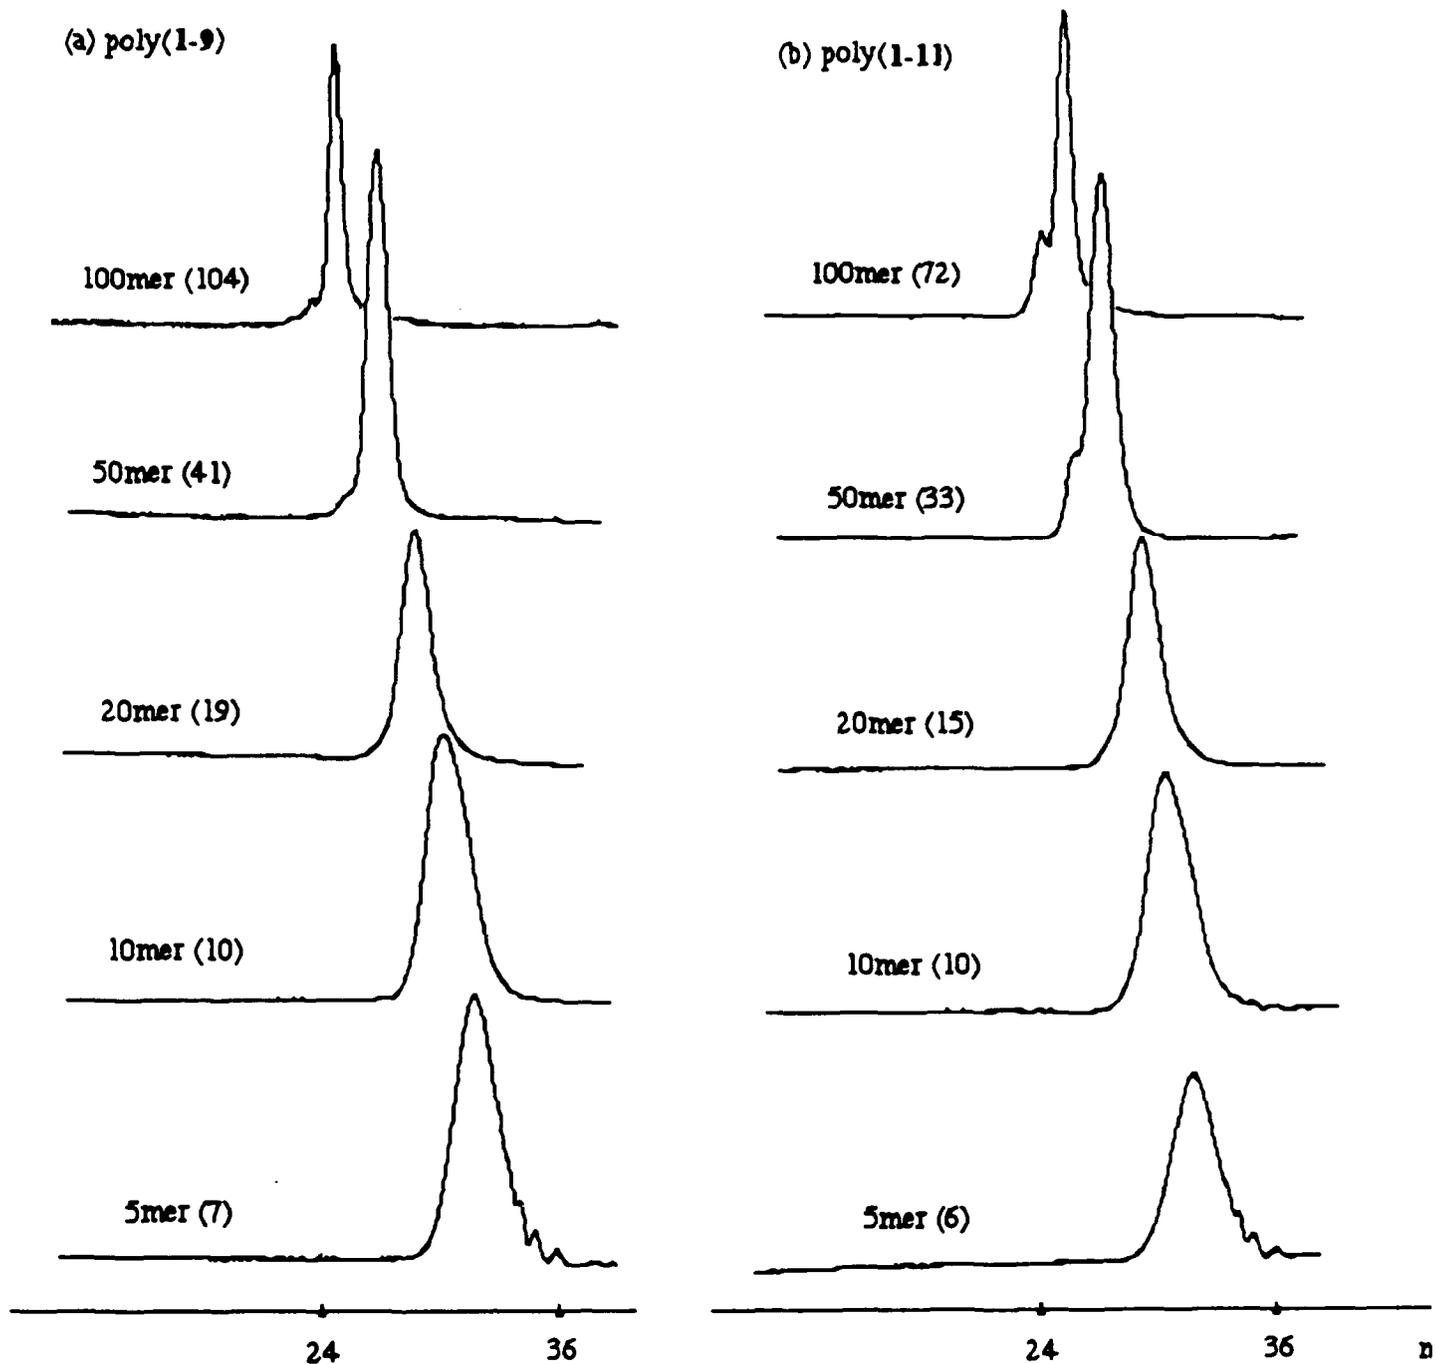


Figure 1. GPC traces of poly(1-9)(a) and poly(1-11)(b).

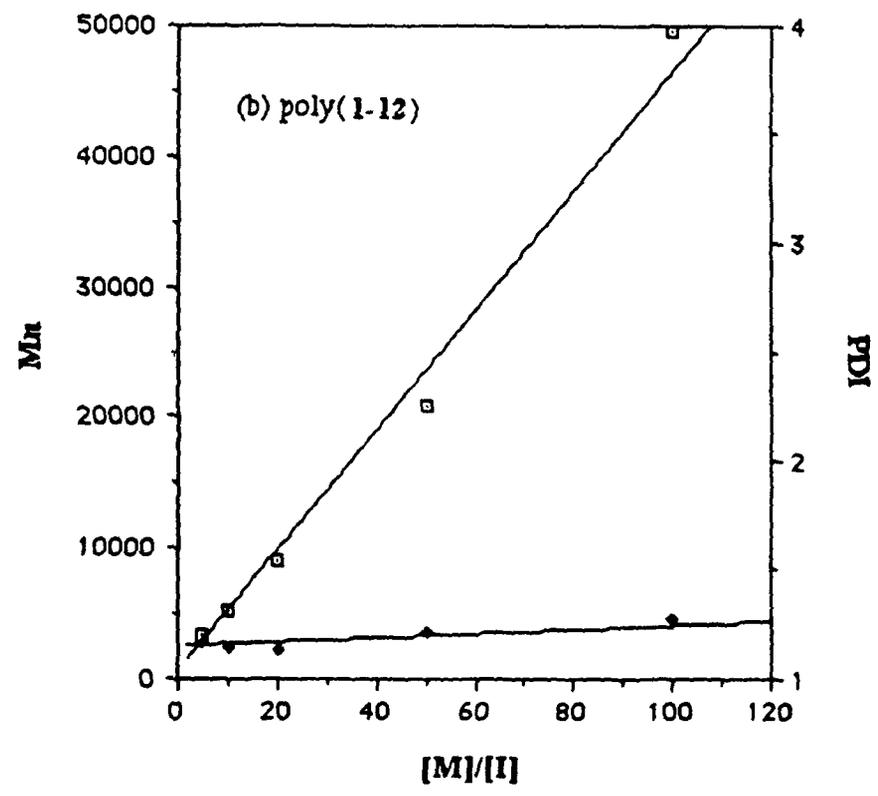
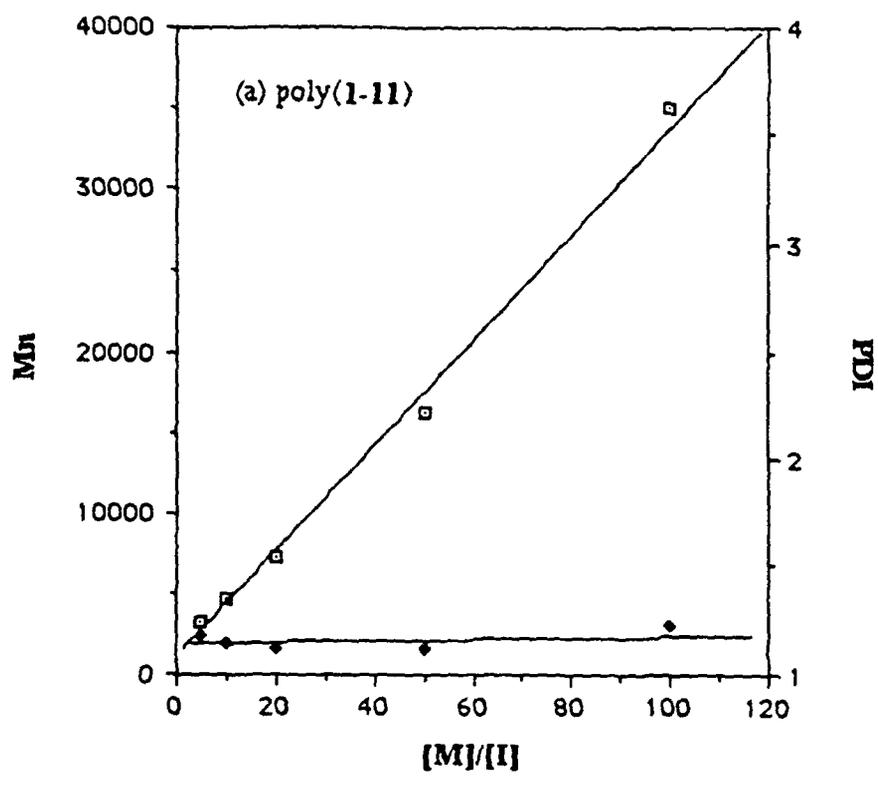


Figure 2. Monomer/catalyst vs Molecular weight

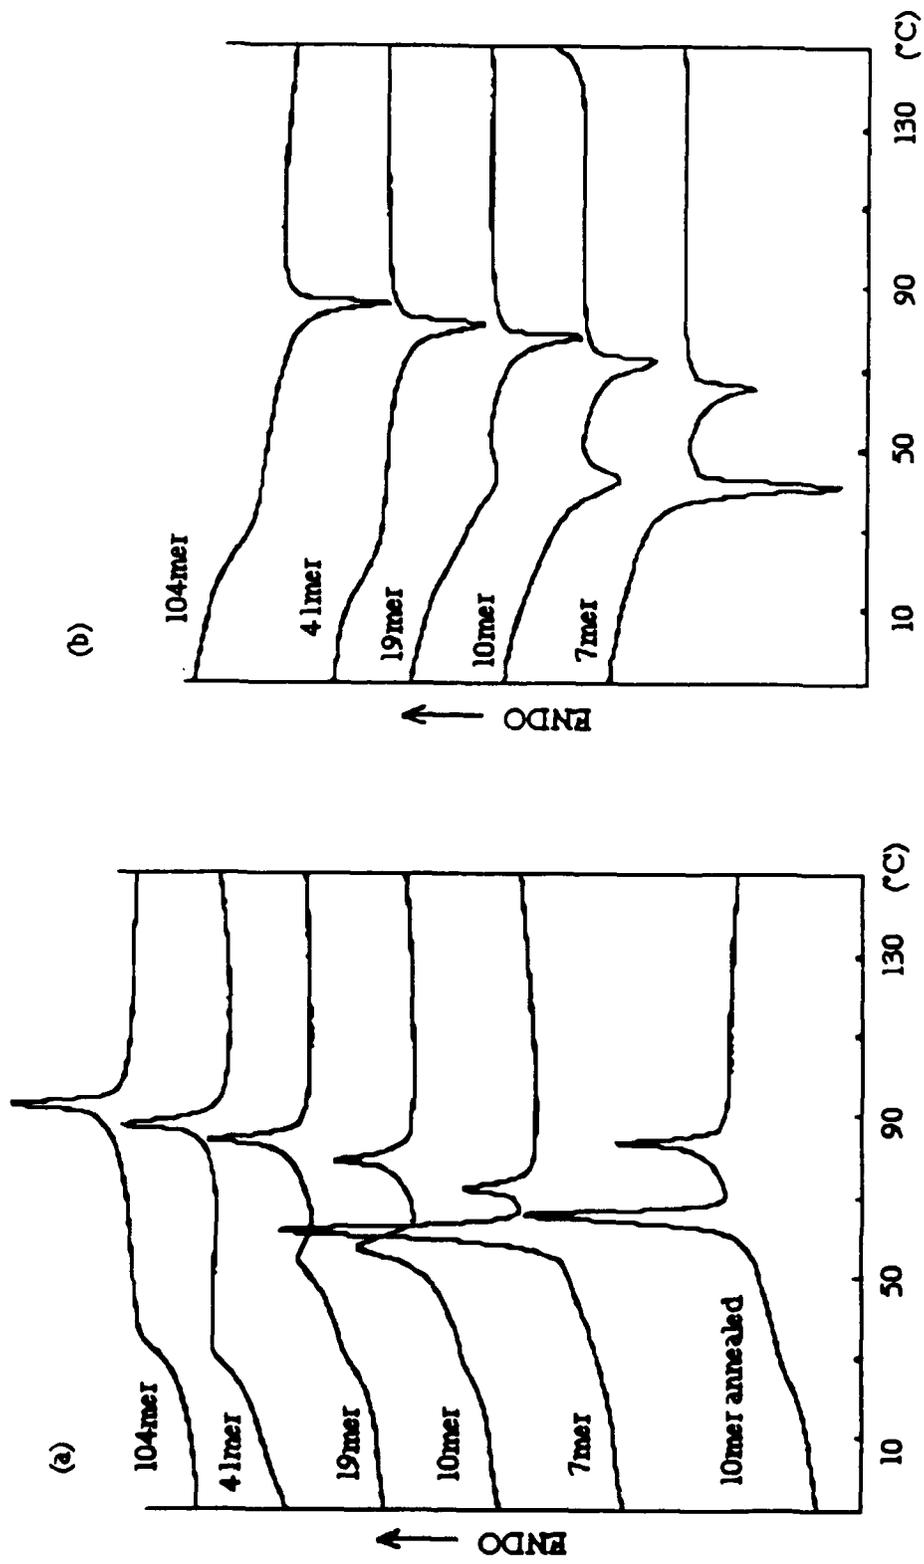


Figure 3. DSC traces of poly(1-9)

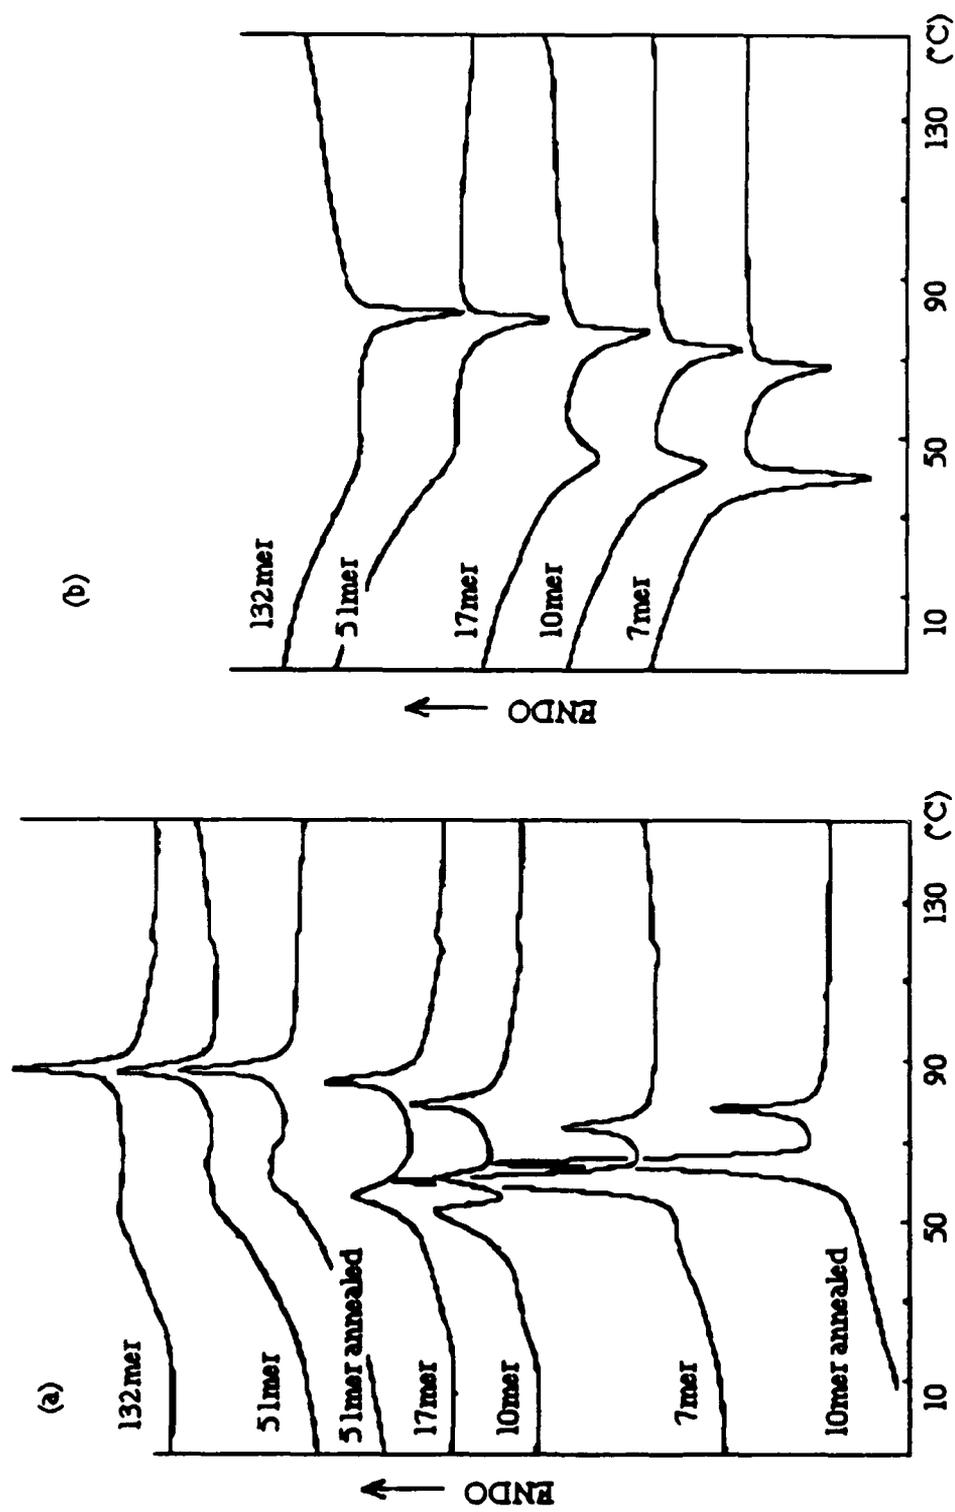


Figure 4. DSC traces of poly(1-10).

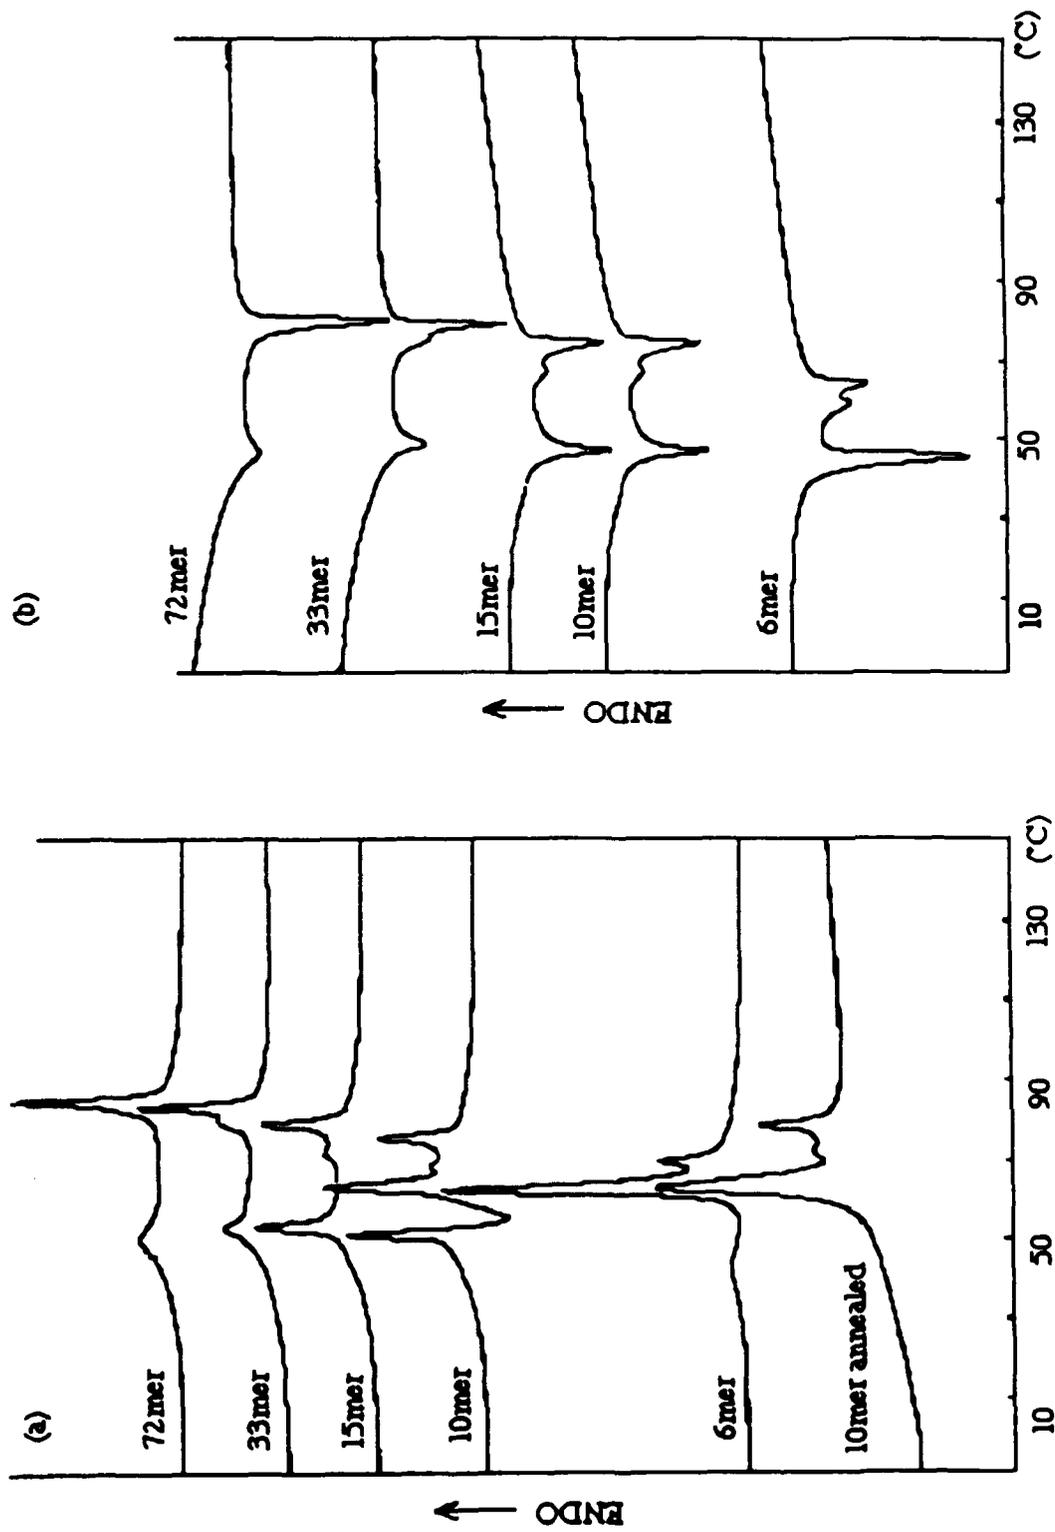


Figure 5 DSC traces of poly(1-11).


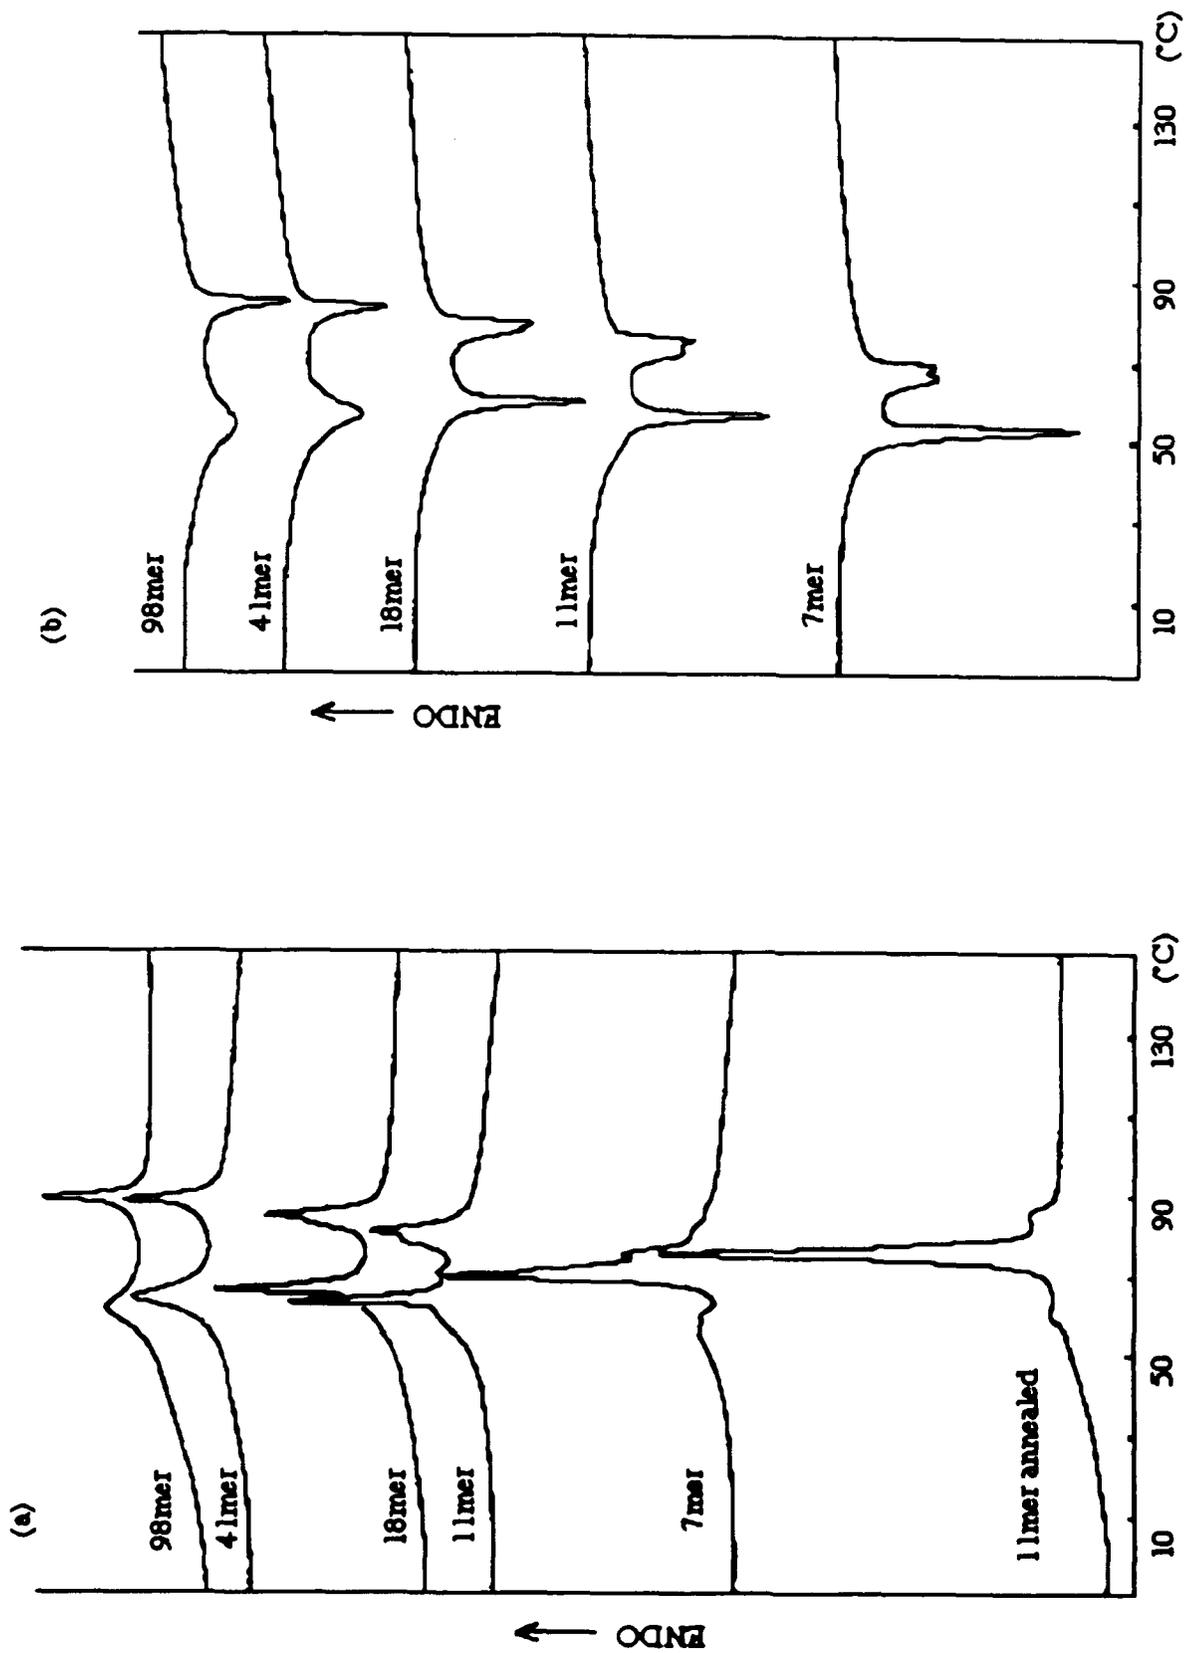


Figure 6. DSC traces of poly(1-12).

(a)

C9, 20mm X80, 80.1°C

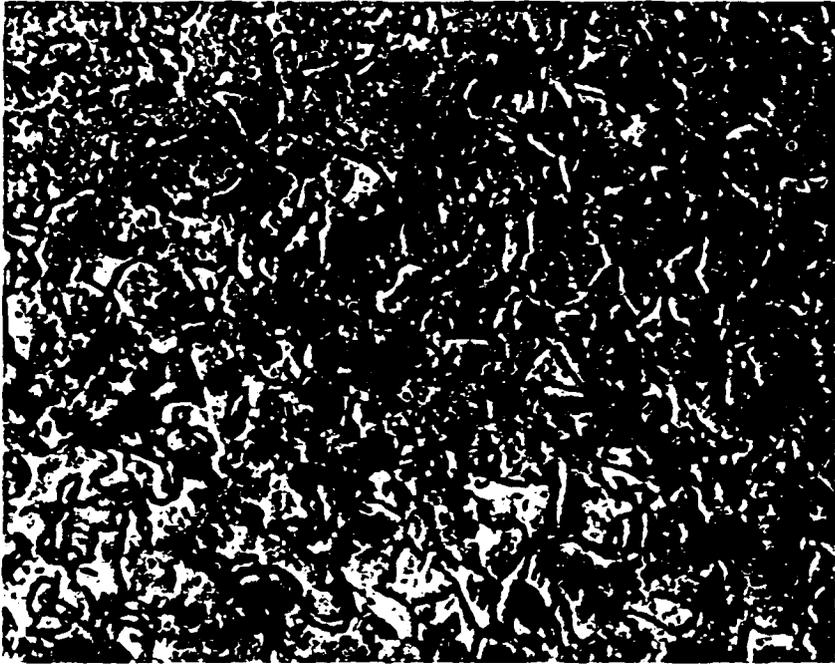

(b)

C11, 50mm X110, 87°C

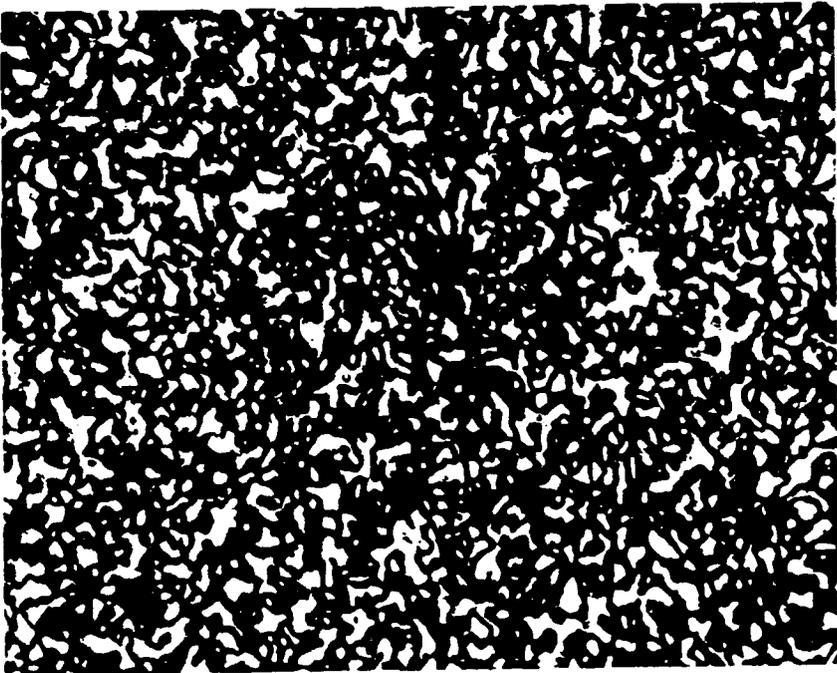


Figure 7

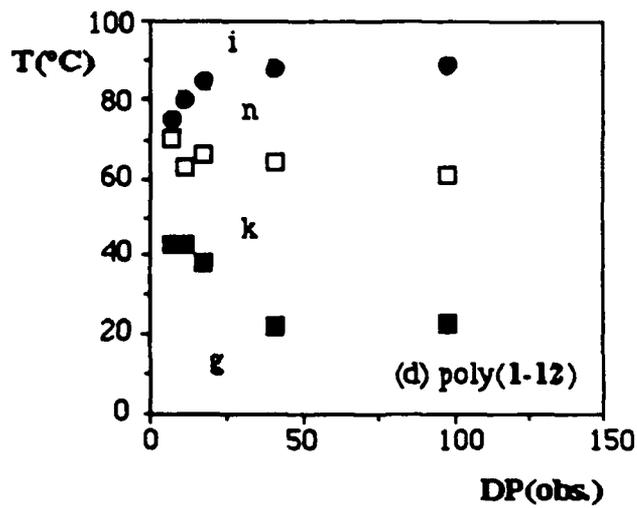
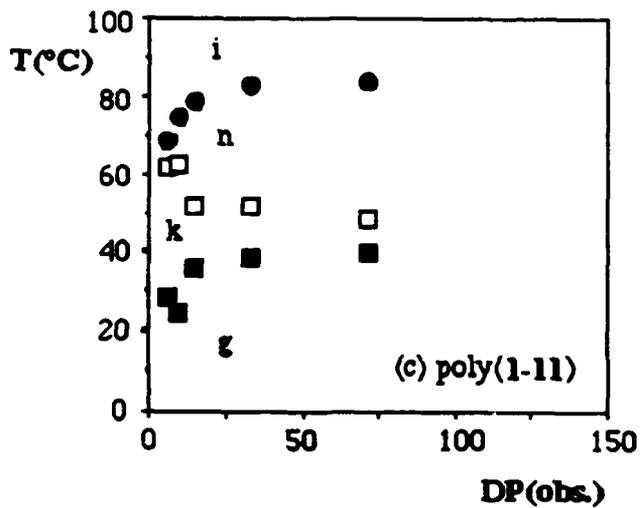
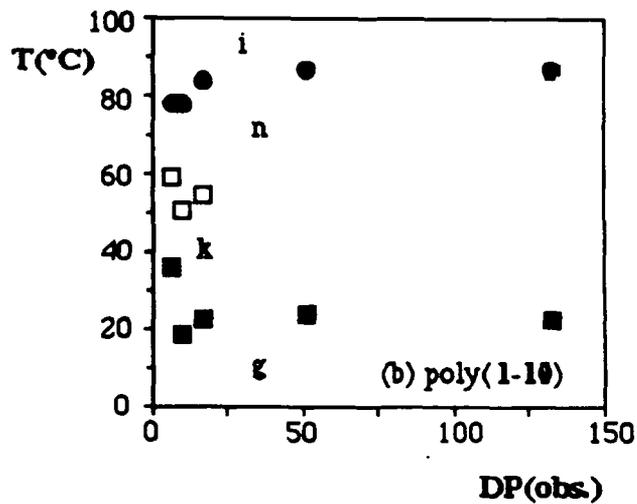
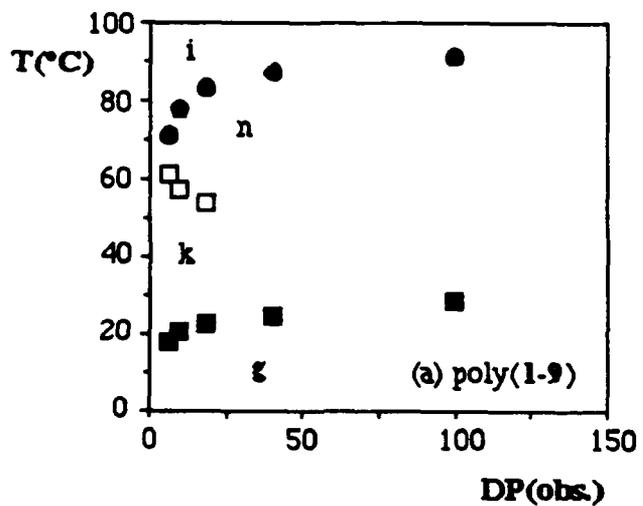


Figure 8.

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)*
Chemistry Division, Code 1113
800 North Quincy Street
Arlington, Virginia 22217-5000

Dr. James S. Murday (1)
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Robert Green, Director (1)
Chemistry Division, Code 385
Naval Air Weapons Center
Weapons Division
China Lake, CA 93555-6001

Dr. Elek Lindner (1)
Naval Command, Control and Ocean
Surveillance Center
RDT&E Division
San Diego, CA 92152-5000

Dr. Bernard E. Douda (1)
Crane Division
Naval Surface Warfare Center
Crane, Indiana 47522-5000

Dr. Richard W. Drisko (1)
Naval Civil Engineering
Laboratory
Code L52
Port Hueneme, CA 93043

Dr. Harold H. Singerman (1)
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Dr. Eugene C. Fischer (1)
Code 2840
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Defense Technical Information
Center (2)
Building 5, Cameron Station
Alexandria, VA 22314

* Number of copies to forward