

AD-A254 661

AGE

Form Approved
OMB No. 0704-0188

Public reporting burd
gathering and maint
collection of inform
Davis Highway, Suite



response, including the time for reviewing instructions, searching existing data sources,
information. Send comments regarding this burden estimate or any other aspect of the
adquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson
Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY US

May 92

3. REPORT TYPE AND DATES COVERED

Final 15 Jul 88-24 Jan 92

4. TITLE AND SUBTITLE

Nanophase Ceramics

DTIC
ELECTE
AUGO 3 1992
S B D

5. FUNDING NUMBERS

DAAL03-88-K-0094

6. AUTHOR(S)

R.S. Averback

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)

University of Illinois Urbana-Champaign
Urbana, IL 61801

8. PERFORMING ORGANIZATION
REPORT NUMBER

9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)

U. S. Army Research Office
P. O. Box 12211
Research Triangle Park, NC 27709-2211

10. SPONSORING / MONITORING
AGENCY REPORT NUMBER

ARO 25526.10-MS

11. SUPPLEMENTARY NOTES

The view, opinions and/or findings contained in this report are those of the
author(s) and should not be construed as an official Department of the Army
position, policy, or decision, unless so designated by other documentation.

12a. DISTRIBUTION / AVAILABILITY STATEMENT

Approved for public release; distribution unlimited.

12b. DISTRIBUTION CODE

13. ABSTRACT (Maximum 200 words)

At the time of initiation of this research, the materials community was just becoming
aware of the pioneering work on nanophase materials by Prof. Gleiter, in Germany, and
the forecasts of new materials with highly desirable properties were being offered. For
ceramic materials, the potential for low temperature sintering and superplastic deformation
were very exciting possibilities, while the effect of nanoscale grain structures on other
properties were also of interest. This research, therefore, was initiated to evaluate the
properties of monolithic, nanophase ceramic materials.

02 7 31 050

175750
92-20771



988

14. SUBJECT TERMS

Ceramics, Nanophase Ceramics, Sintering,
Superplastic Deofrmation, Grain Structures,
Ceramic Materials

15. NUMBER OF PAGES

8

16. PRICE CODE

17. SECURITY CLASSIFICATION
OF REPORT

UNCLASSIFIED

18. SECURITY CLASSIFICATION
OF THIS PAGE

UNCLASSIFIED

19. SECURITY CLASSIFICATION
OF ABSTRACT

UNCLASSIFIED

20. LIMITATION OF ABSTRACT

UL

NANOPHASE CERAMICS

FINAL REPORT ROBERT S. AVERBACK

MAY 21, 1992

U.S. ARMY RESEARCH OFFICE

**CONTRACT: DAAL03 - 88 - K - 0094
PROPOSAL NUMBER: 25526 - MS**

UNIVERSITY OF ILLINOIS URBANA-CHAMPAIGN

FINAL REPORT

Statement of Problem:

At the time of initiation of this research, the materials community was just becoming aware of the pioneering work on nanophase materials by Prof. Gleiter, in Germany, and the forecasts of new materials with highly desirable properties were being offered. For ceramic materials, the potential for low temperature sintering and superplastic deformation were very exciting possibilities, while the effect of nanoscale grain structures on other properties were also of interest. This research, therefore, was initiated to evaluate the properties of monolithic, nanophase ceramic materials.

Summary of the Most Significant Results:

1. Superplastic deformation in nanophase TiO₂

One of the primary motivations for having studied nanophase ceramics derives from their potential for superplastic deformation. Fig. 1, which illustrates the ductility of TiO₂ in compression, demonstrates that large deformations are, indeed, possible in nanophase ceramics, and at relatively low temperatures, approximately one-half the melting temperature, T_m. This study also began to develop constitutive relations for the deformation. For the generalized equation,

$$\dot{\epsilon} = \frac{A\sigma^n}{d^q} \exp\{-\Delta H/kT\}$$

we have found that $n \approx 3$ and $q \approx 1.5$. The activation enthalpy has not yet been obtained. This work remains the only creep study on a dense nanophase ceramic material. It is noteworthy that the Gleiter group has published that nanophase TiO₂ can be plastically deformed at room temperature, i.e., $T < 0.2T_m$; however, from our investigations we can infer that this was possible only because the density of the samples employed for those experiments were less than 80% dense. Nevertheless, our investigations clearly demonstrates that nanophase ceramics are very conducive to superplastic deformation at $T \approx 0.5 T_m$, which is still quite extraordinary.



Fig. 1 Photograph of a nanophase TiO₂ sample before and after deformation at 800 °C. The cylinder was compacted using sinter-forging; its initial density was > 98% and its grain size was ≈ 40 nm.

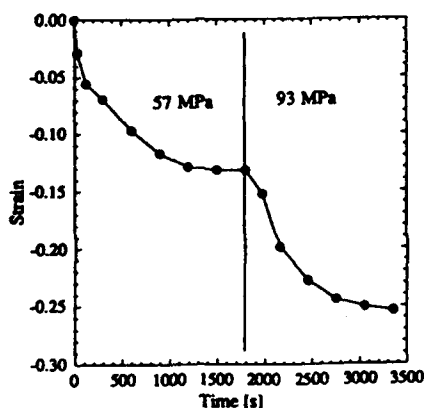


Fig. 2 Change in length of nanophase TiO₂ under uniaxial stress at 650 °C.

DTIC QUALITY INSPECTED 8

ion For	
RA&I	<input checked="" type="checkbox"/>
B	<input type="checkbox"/>
used	<input type="checkbox"/>
ation	<input type="checkbox"/>
tion/	
ility Codes	
Dist	Avail and/or
A-1	Special

An important problem that limits the superplastic response of nanophase ceramics is their propensity for grain growth. We were able to fabricate specimens whose grain sizes in the green body, which was $\approx 78\%$ dense, were less than $\approx 10\text{nm}$, but the grains grew to $\approx 40\text{-}50\text{ nm}$ during densification, and then to $\approx 400\text{ nm}$ during the deformation process that led to the deformed specimen illustrated in Fig. 1. It is clear that methods for controlling the grain size will be required, if these materials are to be used for structural applications where high densities are important.

2. Sinter-forging

One of the methods for enhancing the densification rate during sintering is to apply an external stress. The application of a hydrostatic stress during sintering, i.e., hipping, has long been used for this purpose. The application of a uniaxial stress, however, can also be beneficial. For example, the specimen illustrated in Fig.1 was densified at $600\text{ }^\circ\text{C}$ to nearly full density, while the grain size increased from 10 nm to 40 nm . Sintering of similar specimens without an applied stress revealed that complete densification could not be achieved below $\approx 950\text{ }^\circ\text{C}$, and at that temperature, the grain size had increases to $\approx 0.5\text{ }\mu\text{m}$. In addition to providing a convenient and efficient means to enhance sintering, sintering-forging provides fundamental information about the deformation mechanisms in the material.

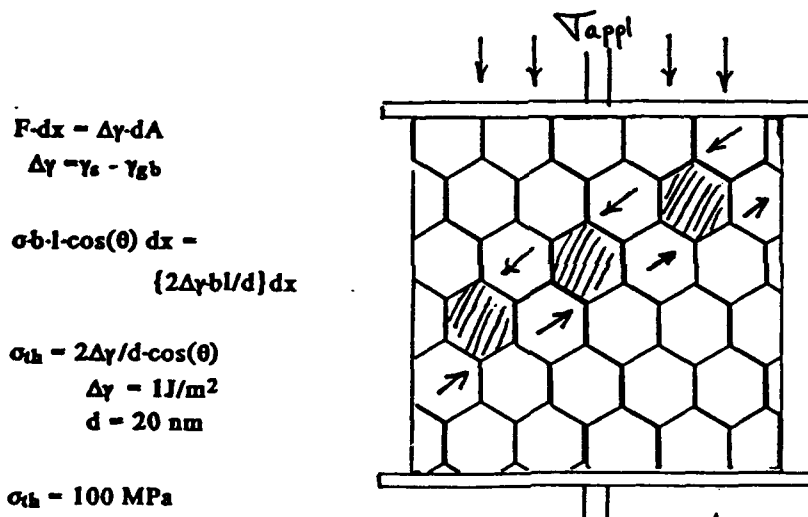


Fig.3 Model of grain boundary sliding during sinter-forging

Fig. 2 illustrates the densification of nanophase TiO_2 during sinter-forging; it shows the change in length of a nanophase TiO_2 cylinder as a function of time. It should be noticed that the densification takes place at $650\text{ }^\circ\text{C}$, which is $< 0.5 T_m$; similar results were obtained at $600\text{ }^\circ\text{C}$, as well. The data in Fig. 2 also show that the densification does not go to completion at the applied stress of 57 MPa , but rather a "metastable" density is obtained. The metastable density was found to be a function of applied stress and temperature. The existence of a threshold stress observed in these sinter-forging experiments appears to be unique to nanophase materials. Although we are still in the process of developing a model to describe this phenomenon, we feel the threshold stress is a consequence of grain boundary sliding as illustrated in Fig.3. In this simplified picture of sinter-forging, it is shown that as grain boundary sliding occurs in the vicinity of a pore, the surface area of the pore increases while grain boundary area decreases, with a net increase in energy. This increase in energy is provided by the work performed by the applied stress. Densification is activated during this process by (i) improving packing of the grains as grains slide past

The fracture toughness of nanophase TiO₂ is plotted in Fig. 7 as a function of grain size. These data were obtained by indentation methods. Clearly shown is that the fracture toughness of the sample is independent of grain size.

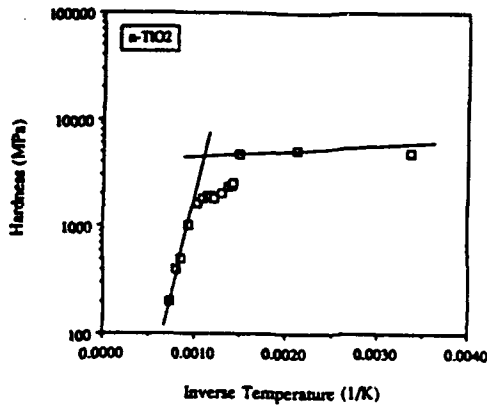


Fig. 6 Vickers microhardness as a function of inverse temperature

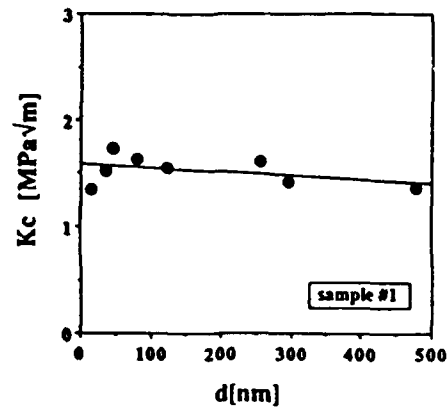


Fig. 7 Fracture toughness K_{1c} as a function of grain size

Sintering of Nanophase TiO₂ and ZrO₂

A thorough investigation of the sintering of nanophase TiO₂ and ZrO₂ was carried out, and it was found that sintering temperatures are reduced by several hundred K relative to μm -sized materials. Below $\approx 900^\circ\text{C}$, both nanophase oxide materials densified with increasing sintering temperature and without significant grain growth. But above this temperature, when the density became greater than $\approx 90\%$, the samples underwent rapid grain growth. For TiO₂, this led to grain sizes of $\approx 1\mu\text{m}$ before full density could be achieved. The ZrO₂ samples, which had a monoclinic structure, became fully dense at similar sintering temperatures, but the grain size remained below $\approx 0.1\mu\text{m}$. Data for the ZrO₂ sample are shown in Fig. 8. Preliminary studies on the effect of impurity doping on grain growth during sintering of TiO₂ were performed, and it was observed that the grain size could be maintained below $\approx 0.1\mu\text{m}$ during densification.

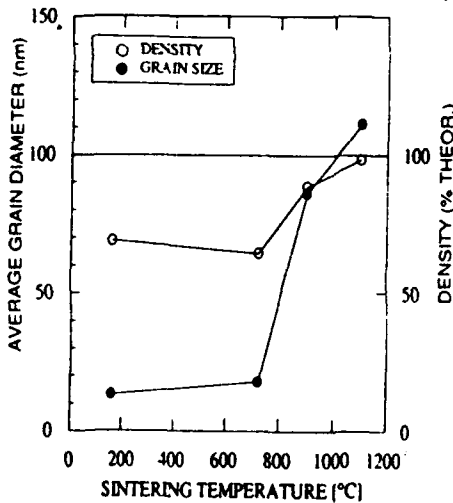


Fig. 9 Grain size and density of nanophase ZrO₂ as a function of sintering temperature

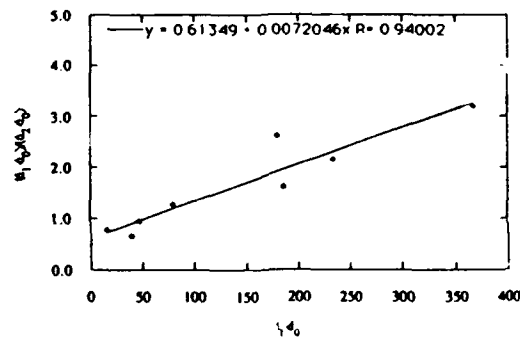


Fig. 10 The ratio of grain sizes in pure and Y-doped nanophase TiO₂ as a function of grain of pure nanophase TiO₂ during isothermal annealing.

each other, (ii) hiping, since the hydrostatic component of the uniaxial stress is $1/3 \sigma_{\text{appl}}$, and (iii) destabilizing the equilibrium shape of the pore and reinitiating sintering. In this simple model, the threshold stress is given by,

$$\sigma_{\text{thresh}} = g \frac{\Delta\gamma}{d}$$

where $\Delta\gamma$ is the difference in the surface and grain boundary energies, g is a geometry factor of order unity, and d is the grain size. Because of the small grain size, $d \approx 10 - 20$ nm, the threshold stress is on the order of 50 - 100 MPa.

Fig. 4 shows the dependence of strain rate on applied stress, and it is seen that the stress exponent ("n" in eq. (1), above) is approximately three. In larger grain ceramic materials, the stress exponent is usually one, again showing the difference between nanocrystalline and microcrystalline materials

Mechanical properties of TiO₂

As part of a survey of the mechanical properties of nanophase ceramic materials, we examined the hardness and fracture toughness of TiO₂ as a function of grain size; the results are illustrated in Figs. 5, 6 and 7. The hardness data reveal two regimes. At larger grain sizes, the Vickers microhardness follows normal Hall-Petch behavior, i.e., the hardness increases as the inverse square root of grain size. However, below a critical size, ≈ 40 nm, the hardness becomes much less sensitive to the grain size, although still increasing slightly with decreasing grain size. In regards to the absolute value of the hardness, the Vickers microhardness of nanophase samples, when fully dense, is somewhat higher, $\approx 25\%$, than bulk samples. The temperature dependence of the hardness is illustrated in in Fig. 6, where it is shown that significant softening begins at temperatures greater than ≈ 400 °C.

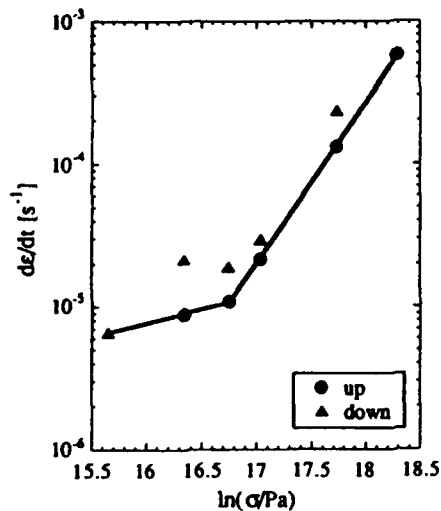


Fig.4 Dependence of strain rate on stress in nanophase TiO₂ during sinter-forging.

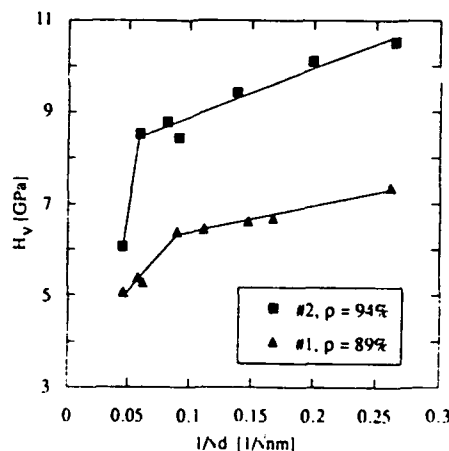


Fig.5 Vickers microhardness as a function of inverse square-root of grain size

Publications:

1. **Microstructure of Nanocrystalline Ceramics**
H. Hahn, J.L. Logas, H.J. Höfler, Th. Bier and R.S. Averback
Mat. Res. Soc. Symp. Vol. 132 (1989).
2. **Kinetic and Thermodynamic Properties of Nanophase Materials,**
R.S. Averback, H. Hahn, H. Höfler, J.L. Logas and T.C. Shen
Mat. Res. Soc. Symp. Vol. 253 (1989) 3.
3. **The Production of Nanocrystalline Powders by Magnetron Sputtering**
H. Hahn and R.S. Averback
J. Appl. Phys. 67 (1990) 1113.
4. **Low Temperature Sintering and Deformation of Nanocrystalline TiO₂**
H. Hahn, P. Kurath and R.S. Averback
Mat. Res. Soc. Symp. Vol. 253 (1989)
5. **Grain Growth in Nanocrystalline TiO₂ and Its Relation to Vickers Hardness and Fracture Toughness**
H.-J. Höfler and R.S. Averback
Scripta Metall. et Mater. 24 (1990) 2401.
6. **Low Temperature Creep of Nanocrystalline TiO₂**
H. Hahn and R.S. Averback
J. Am. Cer. Soc. 74, 4433 (1991).
7. **Temperature Dependence of the Hardness of Nanocrystalline Titanium Dioxide**
M. Guermazi, H.J. Höfler, H. Hahn and R.S. Averback
J. Am. Cer. Soc. 74, (1991) 2672.
8. **Processing and Properties of Nanophase Materials**
R.S. Averback and H.J. Höfler
"Microcomposites and Nanophase Materials," ed. D.C. Van Aken et al. (TMS, Pennsylvania, 1991) p. 27..
9. **Sintering and Deformation of Nanocrystalline Ceramics**
H. Hahn and R.S. Averback, H.J. Höfler and J.C. Logas
Mat. Res. Soc. Symp. Proc. Vol. 206, (1991) p.569.
10. **Sinter-Forging of Nanophase TiO₂**
M. Uchic, H.J. Höfler, W.J. Flick, R. Tao, P. Kurath and R.S. Averback
Scripta. Metall et Mater.
11. **High Temperature Mechanical Properties of Nanostructured Materials**
H. Hahn and R.S. Averback
Nanostructured Materials, 1 (1992) 95.
12. **Sintering Characteristics of Nanophase Ceramics**
R.S. Averback, H.J. Höfler, H. Hahn and J.C. Logas
Nanostructured Materials, 1 (1992) 173.

Developments in Processing Nanophase Ceramics:

During the course of this investigation, some efforts were focused on developing the processing capabilities of nanophase ceramics. A major improvement was the development of a magnetron sputtering system for the production of refractory type materials. The ZrO_2 samples, for example, were produced by first preparing nanophase Zr powder by magnetron sputtering and subsequently oxidizing it. This method is particularly useful when alloy materials are desired since the composition can be well controlled.

A "flow" system for processing nanophase powder was also developed. Unlike the original Gleiter method, which employs thermophoresis for the collection of powder, this system utilizes force flow and collection of the powder in a filter. The system has the advantages that it is conducive to scale up and is cheaper to build.

Papers in progress and initiated under ARO funding:

1. Sinter-forging of Nanophase TiO₂
H.J. Höfler and R.S. Averback
2. Properties of Nanophase ZrO₂
M. Pollack and R.S. Averback

Scientific Personnel:

1. R.S. Averback Principal Investigator
2. H. Hahn Senior Research Associate
3. T.C Shen Research Assistant
4. H.J. Höfler Research Assistant - Research Associate
Received Ph.D. from Universität des Saarlands, Germany;
with partial support from ARO
5. William Flick Research Assistant - currently working on Ph.D.
6. Margolita Pollack Research Assistant - currently working on Ph.D.
7. Rong Tao Laboratory Assistant - currently working on Ph.D.