

AD-A273 557



WL-TR-93-4091



THE MECHANICAL PROPERTY DATA BASE FROM AN
AIR FORCE/INDUSTRY COOPERATIVE TEST PROGRAM ON ADVANCED ALUMINUM
ALLOYS (8090-T8771 PLATE)

MARYANN PHILLIPS and STEVEN R. THOMPSON
Materials Engineering Branch
Systems Support Division

August 1993



Interim Report for Period May 1991 - January 1993

Approved for public release; distribution is unlimited.

Materials Directorate
Wright Laboratory
Air Force Materiel Command
Wright-Patterson Air Force Base, Ohio 45433-7734

93 12 10 003

93-30099



4786

NOTICE


When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely Government-related procurement, the United States Government incurs no responsibility or any obligation whatsoever. The fact that the government may have formulated or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication, or otherwise in any manner construed, as licensing the holder, or any other person or corporation; or as conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.


This report is releasable to the National Technical Information Service (NTIS). At NTIS, it will be available to the general public, including foreign nations.

This Technical report has been reviewed and is approved for publication.


MARY ANN PHILLIPS, Project Engineer
Engineering and Design Data
Materials Engineering Branch


STEVEN R. THOMPSON, Project Engineer
Engineering and Design Data
Materials Engineering Branch


THEODORE J. REINHART, Chief
Materials Engineering Branch
Systems Support Division
Materials Directorate


THOMAS D. COOPER, Chief
Systems Support Division
Materials Directorate
Wright Laboratory

If your address has changed, if you wish to be removed from our mailing list, or if the addressee is no longer employed by your organization, please notify WL/MLSE, WPAFB, OH 45433-7718 to help us maintain a current mailing list.

Copies of this report should not be returned unless return is required by security considerations, contractual obligations, or notice on a specific document.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE August 1993		3. REPORT TYPE AND DATES COVERED Interim 5/91 to 1/93	
4. TITLE AND SUBTITLE The Mechanical Property Data Base from an Air Force/ Industry Cooperative Test Program on Advanced Aluminum Alloys (8090-T8771 Plate)				5. FUNDING NUMBERS PE 62102F PR 2418 TA 07 WU 03	
6. AUTHOR(S) Mary Ann Phillips and Steven R. Thompson (513) 255-5063					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Materials Directorate Wright Laboratory (WL/MLSE) Air Force Materiel Command Wright Patterson Air Force Base OH 45433-7734				8. PERFORMING ORGANIZATION REPORT NUMBER WL-TR-93-4091	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Materials Directorate Wright Laboratory (WL/MLSE) Air Force Materiel Command Wright Patterson Air Force Base OH 45433-7734				10. SPONSORING/MONITORING AGENCY REPORT NUMBER WL-TR-93-4091	
11. SUPPLEMENTARY NOTES					
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for Public Release; distribution is unlimited.				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A mechanical property data base on Alcan produced aluminum-lithium alloy 8090 plate was developed. Mechanical property data consisted of tension, compression, bearing, shear, and fracture toughness properties. Fatigue, fatigue crack growth and spectrum crack growth data were generated.					
14. SUBJECT TERMS Tensile 8090 Aluminum-Lithium		Bearing 2091 Shear AL905XL Compression IN905XL Toughness		15. NUMBER OF PAGES 47	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified		18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified		19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	
				20. LIMITATION OF ABSTRACT UL	

TABLE OF CONTENTS

1.	INTRODUCTION	<u>PAGE</u> 1
2.	MATERIALS AND TESTS	2
3.	PRESENTATION	3
4.	RESULTS AND DISCUSSION	4
5.	CONCLUSIONS	5

Accession For	
NTIS CRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification _____	
By _____	
Distribution /	
Availability Codes	
Dist	Avail and / or Special
A-1	

DTIC QUALITY INSPECTED 3

LIST OF FIGURES

<u>FIGURE</u>	<u>PAGE</u>
F1 Fatigue Results for 8090-T8771 Plate (Longitudinal Orientation). Air Force.	15
F2 Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation). Martin Marietta.	16
F3 Fatigue Crack Growth Rate Data for 8090-T8771 Plate (T-L Orientation). Martin Marietta.	22
F4 Fatigue Crack Growth Rate Data for 8090-T8771 Plate (S-T Orientation). Martin Marietta.	25
F5 Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation and $R = 0.1$). Air Force.	27
F6 Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation and $R = 0.33$). Air Force.	29
F7 Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation, $R = 0.1$ and High Humidity). Air Force.	31
F8 Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation, $R = 0.33$ and High Humidity). Air Force.	34
F9 Mini-TWIST Spectrum Crack Length vs Flights Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 16.9 ksi). Air Force.	35
F10 Mini-TWIST Spectrum Crack Growth Rate vs Delta K Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 16.9 ksi). Air Force.	37
F11 FALSTAFF Spectrum Crack Length vs Total Flights Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 20 ksi). Air Force.	38
F12 FALSTAFF Spectrum Crack Growth Rate vs Delta K Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 20 ksi). Air Force.	39

LIST OF TABLES

<u>TABLE</u>		<u>PAGE</u>
F1	Tensile Results at $t/2$ Location for Alcan 8090-T8771 Plate, Longitudinal Orientation	6
F2	Tensile Results at $t/2$ Location for Alcan 8090-T8771 Plate, 45 Degree Orientation	6
F3	Tensile Results at $t/2$ Location for Alcan 8090-T8771 Plate, Long Transverse Orientation	7
F4	Tensile Results at $t/2$ Location for Alcan 8090-T8771 Plate, Short Transverse Orientation	7
F5	Compression Results at $t/2$ Location for Alcan 8090-T8771 Plate, Longitudinal Orientation	8
F6	Compression Results at $t/2$ Location for Alcan 8090-T8771 Plate, Long Transverse Orientation	8
F7	Compression Results at $t/2$ Location for Alcan 8090-T8771 Plate, Short Transverse Orientation	9
F8	Amsler Double Shear Results at $t/2$ Location for Alcan 8090-T8771 Plate, T-L Orientation	10
F9	Bearing Results at $t/2$ Location for Alcan 8090-T8771 Plate, Longitudinal Orientation and $e/D = 1.5$	11
F10	Bearing Results at $t/2$ Location for Alcan 8090-T8771 Plate, Long Transverse Orientation and $e/D = 1.5$	11
F11	Fracture Toughness Results for Alcan 8090-T8771 Plate, L-T Orientation	12
F12	Fracture Toughness Results for Alcan 8090-T8771 Plate, S-L Orientation	12
F13	Fracture Toughness Results for Alcan 8090-T8771 Plate, T-L Orientation	13
F14	Fracture Toughness Results for Alcan 8090-T8771 Plate, S-T Orientation	13
F15	Fatigue Results with $R = 0.1$ and $K_t = 1.0$ for Alcan 8090-T8771 Plate, Longitudinal Orientation	14
F16	Fatigue Results with $R = 0.1$ and $K_t = 3.0$ for Alcan 8090-T8771 Plate, Longitudinal Orientation	14

LIST OF TABLES CONTINUED

<u>TABLE</u>		<u>PAGE</u>
F17	Fatigue Crack Growth Rate Data Associated with Figure F2 (Specimen CG-LT-1)	17
F18	Fatigue Crack Growth Rate Data Associated with Figure F2 (Specimen CG-LT-2)	19
F19	Fatigue Crack Growth Rate Data Associated with Figure F3 (Specimen CG-TL-1)	23
F20	Fatigue Crack Growth Rate Data Associated with Figure F3 (Specimen CG-TL-2)	24
F21	Fatigue Crack Growth Rate Data Associated with Figure F4 (Specimen CG-ST-2)	26
F22	Fatigue Crack Growth Rate Data Associated with Figure F5	28
F23	Fatigue Crack Growth Rate Data Associated with Figure F6	30
F24	Fatigue Crack Growth Rate Data Associated with Figure F7	32
F25	Fatigue Crack Growth Rate Data Associated with Figure F8	33

PREFACE

This report was prepared by the Materials Engineering Branch (WL/MLSE), Systems Support Division, Materials Directorate, Wright Laboratory, Wright-Patterson Air Force Base, Ohio, under Project 2418, "Metallic Structural Materials," Task 241807, "Systems Support," Work Unit 24180703, "Engineering and Design Data."

The authors would like to thank the participants Martin Marietta LA and the Air Force.

SECTION 1

INTRODUCTION

High performance aerospace systems are dependent on materials that are lighter, have improved mechanical properties, and/or offer a cost savings. Aluminum alloys that met these criteria were the newly developed aluminum-lithium alloys and the second generation powder metallurgy alloys.

In 1985, the Air Force along with the aerospace community found it important to investigate the potential of these promising aluminum alloys. A cooperative program was formed by the Wright Laboratory Materials Directorate, Systems Support Division and a number of aerospace industries. The Air Force would obtain the test material from the producers, compile the test data, and submit reports to the participants. The participants agreed to support the program by performing mechanical property tests which includes tension, compression, bearing, shear, fracture toughness, and fatigue related properties (S/N, da/dn). The Air Force elected to perform spectrum fatigue crack growth testing on most alloys. A list of participants is shown in the following table.

This Interim report contains the aluminum-lithium alloy 8090-T8771 1.75-inch plate produced by Alcan. Comparisons to other materials and ranking of materials are generally avoided since each potential application may be based on different evaluation criteria.

TABLE

Participants and Advanced Aluminum Alloys
in the Cooperative Test Program

PARTICIPANTS	ALUMINUM LITHIUM ALLOYS										PM ALUMINUM ALLOYS	
	PECHINEY 2091 - 13 Sheet (0.0637) 2091 - 131 Plate (0.4507) 2091 - 13 Forging 8090 - 1651 Extrusion	ALCAN 8090 - 1651 Extrusion 8090 - 1671 Plate (1.757) PM 809034L Forging	IncoMAP PM 809034L Forging 2091 - 13 Sheet (0.0637) 2091 - 13 Plate (0.447) 2091 - 13 Forging 8090 Extrusion	ALCOA 2091 - 13 Sheet (0.0637) 2091 - 13 Plate (0.447) 2091 - 13 Forging 8090 Extrusion	REYNOLDS Weldable 6061 R4815 Plate (0.57)	KAISER 7064 - 174511 Extrusion 7064 - 174 Forging CW67 Sheet (0.0637) CW67 Plate (0.407) CW67 Extrusion CW67 Forging	ALCOA CW67 Sheet (0.0637) CW67 Plate (0.407) CW67 Extrusion CW67 Forging					
Air Force WPAFB, OH	x	x	x	x	x	x	x	x	x	x	x	
Army, MA					x							
AVCO, TN				x								
Boeing, WA	x	x	x									
Douglas Aircraft, CA				x	x	x	x	x	x	x	x	
General Dynamics, CA	x	x		x	x	x	x	x	x	x	x	
General Dynamics, TX	x	x	x	x	x	x	x	x	x	x	x	
Grumman Aerospace, NY	x	x	x									
Jet Propulsion, CA				x								
Lockheed, CA	x	x		x	x	x	x	x	x	x	x	
Lockheed, GA	x	x		x	x	x	x	x	x	x	x	
LTV, TX	x	x		x	x	x	x	x	x	x	x	
Martin Marietta, LA	x	x	x	x	x	x	x	x	x	x	x	
McDonnell Douglas Astro, CA				x								
McDonnell Douglas Helicopter, AR				x								
McDonnell Douglas Missile Sys, MO												
McDonnell Aircraft, MO	x			x	x	x	x	x	x	x	x	
NASA, VA			x	x	x	x	x	x	x	x	x	
Naval Air Development Center	x	x		x	x	x	x	x	x	x	x	
Northrop, CA	x	x	x	x	x	x	x	x	x	x	x	
Sikorsky, CT				x								
Sundstrand, IL												
Wyman-Gordon				x								

SECTION 2

MATERIALS AND TESTS

The Alcan aluminum-lithium alloy 8090-T8771 1.75-inch plate was received May 1991. The 8090 was tested in the as-received condition by Martin Marietta and the Air Force.

Mechanical properties (tension, compression, bearing shear and fracture toughness), fatigue and constant amplitude fatigue crack growth tests were performed according to ASTM standards, unless otherwise specified. Spectrum fatigue crack growth tests were performed by the Air Force using FALSTAFF (a severe fatigue environment) and Mini-TWIST (a moderately intense fatigue environment) spectrums.

SECTION 3

PRESENTATION

Each participant compiled a data package which contained the data they generated. Some of these data packages contain discussion, and in other cases, only the data were provided. The tensile, compression, bearing, shear and fracture toughness data are put in tabular form. Fatigue, fatigue crack growth and spectrum fatigue crack growth data were put in tabular and graphical form.

SECTION 4

RESULTS AND DISCUSSION

The data generated by the participants on the 8090 plate are shown in Tables F1 thru F25 and Figures F1 thru F12.

SECTION 5

CONCLUSIONS

Two aerospace laboratories participated in generating data on the Alcan 8090-T8771 Plate for the cooperative test program. These data combined with previous interim reports on the Air Force/Industry Cooperative Test Program on Advanced Aluminum Alloys provide an extensive data base on aluminum-lithium alloys.

TABLE F1

TENSILE RESULTS AT t/2 LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	TEST TEMP (DEGREES F)	ORIENT- ATION	ULTIMATE STRENGTH (KSI)	YIELD STRENGTH (KSI)	ELONG (%)	RA (%)	E (MSI)
MARTIN	RT	LONG	79.1	71.0	5.0	3.9	
MARIETTA			79.1	71.2	5.0	9.6	
			79.3		5.0	3.5	
AIR FORCE	RT	LONG	76.7	65.7	8.1	9.2	
			80.2	72.6	5.5	5.2	
			76.7	66.0	7.9	11.6	
		AVERAGE	78.5	69.3	6.1	7.2	
		STANDARD DEVIATION	1.5	3.2	1.5	3.4	

TABLE F2

TENSILE RESULTS AT t/2 LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	TEST TEMP (DEGREES F)	ORIENT- ATION	ULTIMATE STRENGTH (KSI)	YIELD STRENGTH (KSI)	ELONG (%)	RA (%)	E (MSI)
AIR FORCE	RT	45	72.3	54.7	11.5	17.6	
			72.4	58.0	8.9	14.5	
			72.5	55.5	9.8	15.4	
		AVERAGE	72.4	56.1	10.0	15.8	
		STANDARD DEVIATION	0.1	1.7	1.3	1.6	

TABLE F3

TENSILE RESULTS AT $t/2$ LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	TEST TEMP (DEGREES F)	ORIENT- ATION	ULTIMATE STRENGTH (KSI)	YIELD STRENGTH (KSI)	ELONG (%)	RA (%)	E (MSI)
MARTIN MARIETTA	RT	L TRANS	78.2 78.1 78.5	66.9 66.8 67.1	6.0 6.0 6.0	8.1 8.9 8.5	
AIR FORCE	RT	L TRANS	73.3 79.5 73.8	56.9 68.4 57.3	10.4 6.5 10.5	10.3 9.7 11.2	
		AVERAGE	76.9	63.9	7.6	9.4	
		STANDARD DEVIATION	2.7	5.3	2.2	1.2	

TABLE F4

TENSILE RESULTS AT $t/2$ LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	TEST TEMP (DEGREES F)	ORIENT- ATION	ULTIMATE STRENGTH (KSI)	YIELD STRENGTH (KSI)	ELONG (%)	RA (%)	E (MSI)
AIR FORCE	RT	S TRANS	75.6 75.0 75.8	61.4 61.0 62.0	1.7 3.5 5.4	2.4 2.4 5.1	
		AVERAGE	75.4	61.5	3.5	3.3	
		STANDARD DEVIATION	0.4	0.5	1.8	1.6	

TABLE F5

COMPRESSION RESULTS AT $t/2$ LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	TEST TEMPERATURE (DEGREES F)	ORIENTATION	COMPRESSIVE YIELD STRENGTH (KSI)	COMPRESSIVE MODULUS (KSI)
MARTIN	RT	LONG	70.3	12.1
MARIETTA			67.0	12.1
			68.1	12.1
AIR FORCE	RT	LONG	62.5	11.8
			63.9	12.0
			60.5	10.1
		AVERAGE	65.4	11.7
		STANDARD DEVIATION	3.7	0.8

TABLE F6

COMPRESSION RESULTS AT $t/2$ LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	TEST TEMPERATURE (DEGREES F)	ORIENTATION	COMPRESSIVE YIELD STRENGTH (KSI)	COMPRESSIVE MODULUS (KSI)
MARTIN	RT	L TRANS	72.6	12.2
MARIETTA			73.6	12.0
			73.1	12.1
AIR FORCE	RT	L TRANS	62.5	11.8
			70.9	12.0
			67.5	11.9
		AVERAGE	70.0	12.0
		STANDARD DEVIATION	4.3	0.1

TABLE F7

COMPRESSION RESULTS AT $t/2$ LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	TEST TEMPERATURE (DEGREES F)	ORIENTATION	COMPRESSIVE YIELD STRENGTH (KSI)	COMPRESSIVE MODULUS (KSI)
MARTIN	RT	S TRANS	69.6	12.1
MARIETTA			68.8	12.0
			68.5	12.0
		AVERAGE	69.0	12.0
		STANDARD DEVIATION	0.6	0.1

TABLE F8
 AMSLER DOUBLE SHEAR RESULTS AT $t/2$ LOCATION FOR
 ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	SHEAR STRENGTH (KSI)
AIR FORCE	T-L	41.1
		41.8
		43.4
		44.4
		43.6
		41.4
	AVERAGE	42.6
	STANDARD DEVIATION	1.4

TABLE F9

BEARING RESULTS AT $t/2$ LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	e/D	BEARING	
			ULT. STR. (KSI)	BEARING YIELD STR. (KSI)
AIR FORCE	LONG	1.5	112.1	90.6
			112.8	91.5
			106.9	83.7
			AVERAGE	
			110.6	88.6
STANDARD DEVIATION		3.2	4.3	

TABLE F10

BEARING RESULTS AT $t/2$ LOCATION FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	e/D	BEARING	
			ULT. STR. (KSI)	BEARING YIELD STR. (KSI)
AIR FORCE	L TRANS	1.5	109.9	89.6
			112.7	90.6
			105.7	87.3
AVERAGE			109.4	89.2
STANDARD DEVIATION			3.5	1.7

TABLE F11
FRACTURE TOUGHNESS RESULTS FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	KIC (KSI in^0.5)	Kq (KSI in^0.5)	COMMENT

MARTIN MARIETTA	L-T		29.9	(1)
			27.9	(1)
			28.3	(1)
AIR FORCE	L-T		24.7	(2)
			23.7	(2)
		27.0		
	AVERAGE	27.0	26.9	
	STANDARD DEVIATION	0.0	2.6	

(1): INVALID DUE TO $a/W < 0.45$
(2): INVALID DUE TO $P_{max}/P_q > 1.1$

TABLE F12
FRACTURE TOUGHNESS RESULTS FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	KIC	Kq	COMMENT
		(KSI in^0.5)	(KSI in^0.5)	
MARTIN MARIETTA	S-L		11.1	(1)
			11.0	(1)
AIR FORCE	S-L		12.1	(1)
			12.8	(1)
			9.9	(1), (2)
	AVERAGE		11.8	
	STANDARD DEVIATION		0.9	

(1): INVALID DUE TO $K_{fat}/K_q > 0.6$
(2): INVALID DUE TO $a, B < 2.5(K_q/Y_S)^2$

TABLE F13

FRACTURE TOUGHNESS RESULTS FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	KIC (KSI in ^{0.5})	Kq (KSI in ^{0.5})	COMMENT
MARTIN MARIETTA	T-L		21.0 20.1	(1) (1)
AIR FORCE	T-L	25.0 24.3 22.7		
	AVERAGE	24.0	20.6	
	STANDARD DEVIATION	1.2	0.6	

(1): INVALID DUE TO $K_{fat}/K_q > 0.6$

TABLE F14

FRACTURE TOUGHNESS RESULTS FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	KIC (KSI in ^{0.5})	Kq (KSI in ^{0.5})	COMMENT
MARTIN MARIETTA	S-T		13.1	(1)
	AVERAGE		13.1	
	STANDARD DEVIATION		0.0	

(1): INVALID DUE TO $K_{fat}/K_q > 0.6$

TABLE F15

FATIGUE RESULTS WITH $R=0.1$ AND $K_t=1.0$ FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	STRESS (KSI)	CYCLES
AIR FORCE	LONG	73.5	5,016
		69.0	15,020
		66.0	16,366
		60.0	36,998
		57.0	93,383
		50.8	280,000
		48.0	95,642
		43.5	2,946,918
		37.5	17,000,000 *
		29.0	10,000,000 *

(*): RUN OUT

TABLE F16

FATIGUE RESULTS WITH $R=0.1$ AND $K_t=3.0$ FOR
ALCAN 8090-T8771 PLATE (1.75" THICK)

COMPANY	ORIENTATION	STRESS (KSI)	CYCLES
AIR FORCE	LONG	50.0	3,822
		40.0	7,994
		30.0	32,103
		28.0	39,796
		26.0	74,224
		24.0	64,517
		22.0	135,951
		21.0	648,867
		20.5	103,502
		20.0	10,000,000 *

(*): RUN OUT

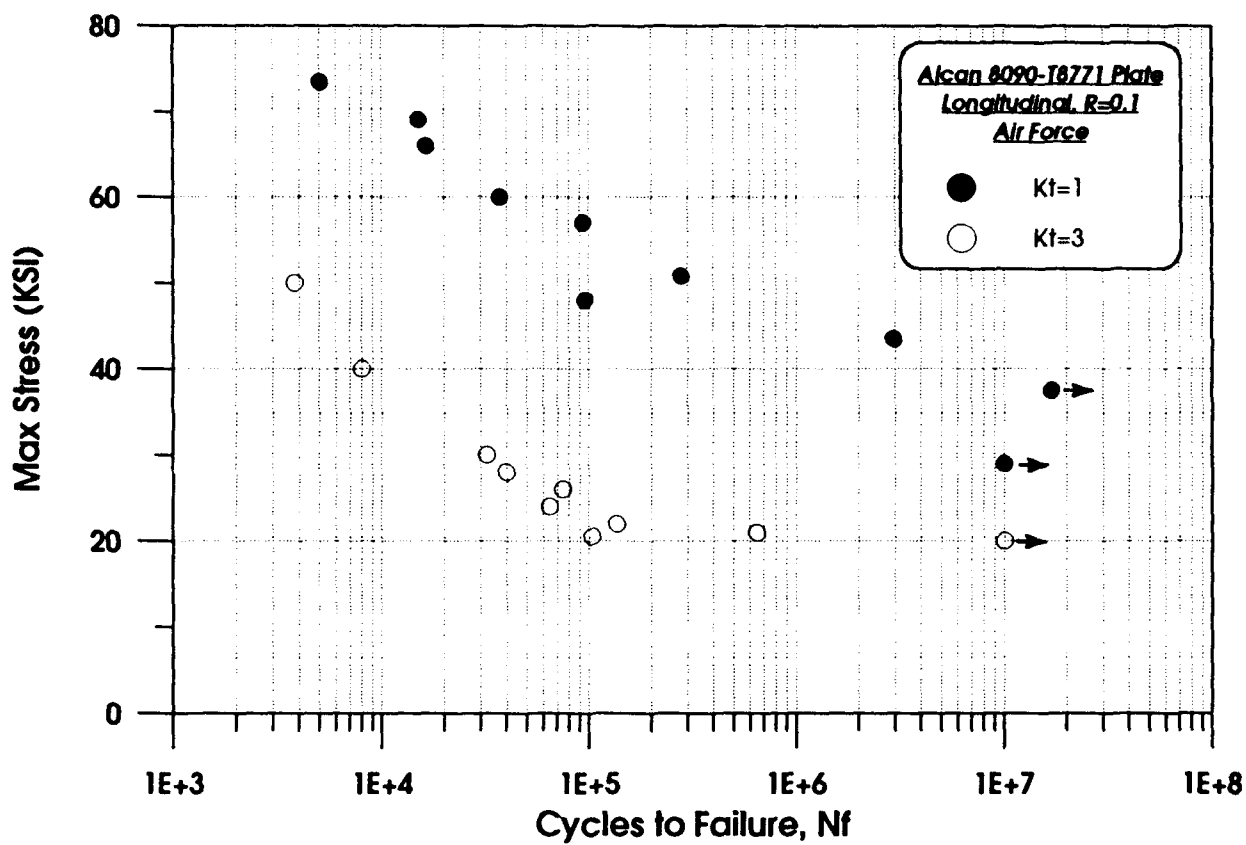


FIGURE F1. Fatigue Results for 8090-T8771 Plate (Longitudinal Orientation).
Air Force.

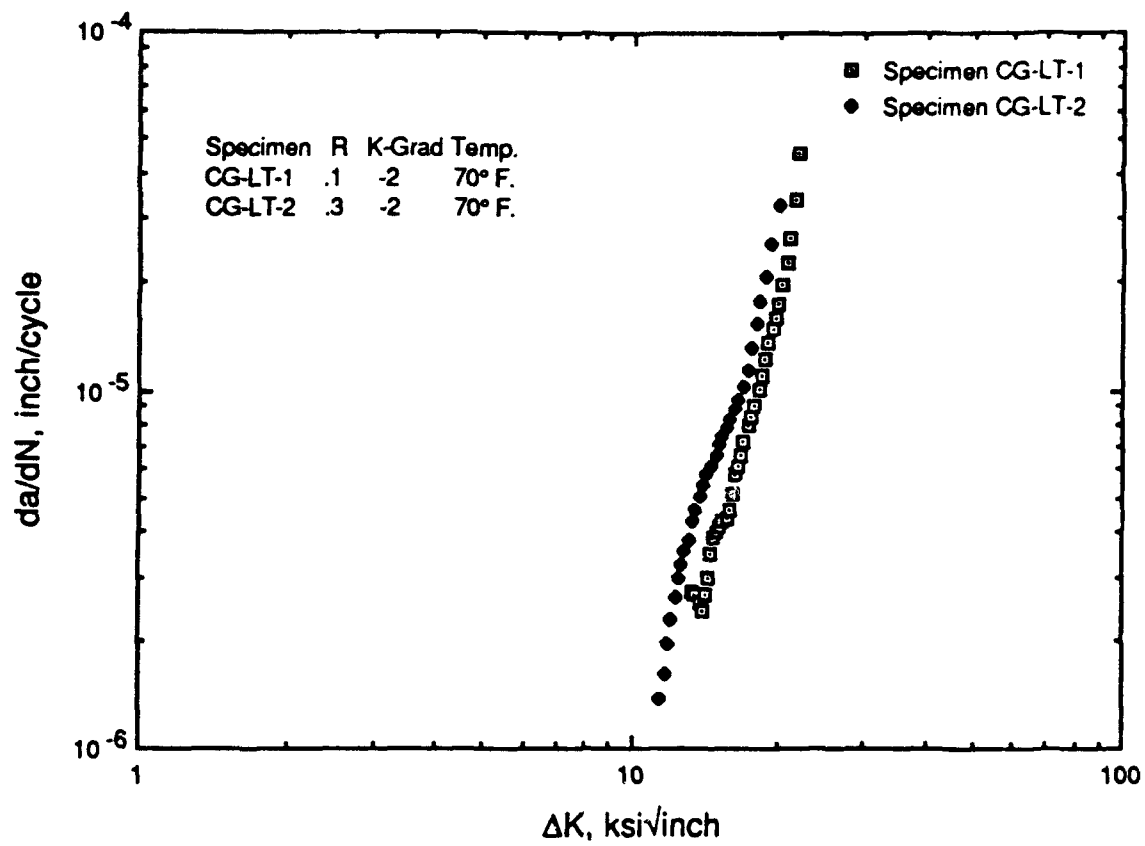


FIGURE F2. Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation).
 Martin Marietta.

TABLE F17

Fatigue Crack Growth Rate Data Associated with
Figure F2 (Specimen CG-LT-1)

Tests were performed with the "CGR Crack Growth Program" from Interlaken Version 1.0B.
Strengths are in PSI. Loads in pounds. Dimensions in inches. Temperature in Degrees Fahrenheit. dK in psi sqrt inch.
The crack lengths were corrected based on the final measurements. The data was averaged using the 7 pt. polynomial method.
The precrack Pmax load of 2875 lbs. was 6.8% higher than the initial Pmax test load of 2446 lbs.

Operator:	cpm
Sample date:	09-24-91
Material:	8090 Al-Li
ID #:	CG-LT-1
Yield Strength:	71110
Modulus of Elast:	11100000
COD Pos:	2
Crack Plane:	L-T
Geometry:	1
Width:	2.0035
Thickness:	1.001
Half span (MT):	.1
Env:	AIR
Temp:	70
Humidity:	50
Waveform:	1
Test Frequency:	10
Test Type:	1
K Gradient:	-2
Min Load:	270
Max Load:	2700
Test Mode:	1
Data Pt Intvl:	.01
Min Growth Rate:	.00001
Compl Slope:	2
Pts/Cycle:	200
Upper Slope Limit:	85
Lower Slope Limit:	15
No of Slopes Ave:	5
Compliance Cor.:	1.01186
Notch Length:	.804
Precrack Length:	.892
Precrack Cycles:	95360
Precrack Max Load:	2874.94
Precrack Min Load:	283.341
#Points:	40

TABLE F17 Continued

#Points: cycle	crack length	dA/dN	dK	Delta Load
76	.81807	0	0	2446.02
7687	.827839	0	0	2431.85
11622	.837417	0	0	2429.41
16621	.847308	2.73482e-6	13341.6	2430.87
17016	.857309	2.74944e-6	13378.2	2428.92
21521	.867043	2.678e-6	13622.4	2430.39
25456	.876509	2.55124e-6	13808.4	2430.39
29962	.886573	2.40983e-6	13993.8	2429.41
34874	.896374	2.67777e-6	14239.5	2431.36
37578	.905701	2.99468e-6	14373.	2430.39
40855	.915003	3.49581e-6	14580.9	2430.87
43805	.924823	3.89369e-6	14815.8	2431.36
45858	.934519	4.03748e-6	14983.	2429.9
48074	.944946	4.21119e-6	15198.9	2429.9
50372	.954235	4.33896e-6	15428.7	2430.39
52833	.964569	4.38178e-6	15659.4	2429.9
55293	.974571	4.67815e-6	15910.7	2430.87
57427	.984776	5.17769e-6	16146.	2429.9
59238	.994184	5.80673e-6	16382.4	2430.39
60801	1.00372	6.16529e-6	16634.7	2431.85
62365	1.01396	6.59573e-6	16884.2	2429.9
63602	1.02362	7.22593e-6	17103.3	2429.9
65247	1.03348	7.97268e-6	17438.7	2430.39
66486	1.04331	8.4522e-6	17729.2	2431.36
67396	1.05402	9.04237e-6	17958.	2432.34
68552	1.0638	1.00304e-5	18294.9	2432.83
69626	1.07315	1.10796e-5	18619.3	2431.85
70374	1.08258	1.22187e-5	18850.5	2429.9
71203	1.09293	1.35224e-5	19194.1	2429.9
71869	1.10246	1.47645e-5	19525.2	2431.36
72454	1.112	1.58668e-5	19824.3	2431.35
73120	1.12168	1.75657e-5	20185.2	2428.92
73623	1.13112	1.96805e-5	20523.9	2432.34
74126	1.1409	2.26089e-5	20831.3	2429.9
74548	1.15039	2.67701e-5	21254.3	2431.36
74970	1.16217	3.40151e-5	21720.9	2433.32
75310	1.17278	4.57042e-5	22056.1	2432.34
75569	1.18441	0	0	2431.36
75828	1.19962	0	0	2433.32
76005	1.2165	0	0	2434.29

TABLE F18

Fatigue Crack Growth Rate Data Associated
with Figure F2 (Specimen CG-LT-2)

Tests were performed with the "CGR Crack Growth Program" from Interlaken Version 1.0B.
Strengths are in PSI. Loads in pounds. Dimensions in inches. Temperature in Degrees Fahrenheit. dK in psi sqrt inch.
The crack lengths were corrected based on the final measurements. The data was averaged using the 7 pt. polynomial method.
The precrack Pmax load of 2875 lbs. was 6.8% higher than the initial Pmax test load of 1936 lbs.

Operator:	cpm
Sample date:	09-24-91
Material:	8090 Al-Li
ID #:	CG-LT-2
Yield Strength:	71110
Modulus of Elast:	11100000
COD Pos:	2
Track Plane:	L-T
Geometry:	1
Width:	2.003
Thickness:	1
Half span (MT):	.1
Env:	AIR
Temp:	70
Humidity:	50
Waveform:	1
Test Frequency:	10
Test Type:	1
K Gradient:	-2
Min Load:	810
Max Load:	2700
Test Mode:	1
Data Pt Intvl:	.01
Min Growth Rate:	.00001
Compl Slope:	2
Pts/Cycle:	200
Upper Slope Limit:	85
Lower Slope Limit:	15
No of Slopes Ave:	5
Compliance Cor.:	1.06142
Notch Length:	.8035
Precrack Length:	.897
Precrack Cycles:	66865
Precrack Max Load:	2874.94
Precrack Min Load:	862.237
#Points:	36

TABLE F18 Continued

#Points: cycle	crack length	³⁶ dA/dN	dK	Delta Load
76	.891065	0	0	1936.49
169	.90337	0	0	1896.43
13388	.914341	0	0	1891.55
22926	.925698	1.38423e-6	11527.9	1891.06
31815	.93633	1.62176e-6	11725.2	1890.08
38017	.946829	1.95346e-6	11894.8	1889.11
42836	.957324	2.30119e-6	12063.3	1889.59
47326	.967997	2.64268e-6	12276.8	1892.04
51251	.978596	2.99747e-6	12477.5	1892.04
54847	.990381	3.27357e-6	12675.3	1889.59
58281	1.00171	3.58152e-6	12920.	1891.55
60900	1.01242	3.85038e-6	13124.9	1893.01
64008	1.02339	4.29105e-6	13355.5	1890.08
66382	1.03392	4.64784e-6	13594.2	1892.53
68676	1.04479	5.08078e-6	13838.6	1893.5
70644	1.05635	5.44453e-6	14064.9	1891.55
72776	1.06732	5.85194e-6	14341.3	1891.06
74419	1.07784	6.16975e-6	14577.6	1891.06
76223	1.08847	6.60149e-6	14861.	1892.04
77784	1.09948	7.08273e-6	15124.8	1891.06
79346	1.11034	7.45266e-6	15419.6	1890.57
80663	1.12107	7.86935e-6	15709.6	1892.04
81979	1.13184	8.25386e-6	16009.4	1892.53
83377	1.14275	8.83869e-6	16351.3	1892.53
84531	1.15341	9.46722e-6	16655.9	1892.53
85685	1.16417	1.0335e-5	16991.7	1891.55
86676	1.17499	1.15143e-5	17354.6	1894.48
87667	1.18639	1.32648e-5	17722.9	1892.53
88496	1.19695	1.53373e-5	18106.9	1892.04
89162	1.20782	1.78032e-5	18478.7	1892.04
89745	1.21887	2.09292e-5	18887.2	1894.48
90329	1.2306	2.56765e-5	19370.7	1894.97
90832	1.24363	3.3126e-5	19961.9	1894.48
91172	1.25502	0	0	1898.39
91430	1.26608	0	0	1897.9
91688	1.28	0	0	1896.43

TABLE F18 Continued

#Points: cycle	crack length	dA/dN	dK	Delta Load
76	.891065	0	0	1936.49
169	.90337	0	0	1896.43
13388	.914341	0	0	1891.55
22926	.925698	1.38423e-6	11527.9	1891.06
31815	.93633	1.62176e-6	11725.2	1890.08
38017	.946829	1.95346e-6	11894.8	1889.11
42836	.957324	2.30119e-6	12063.3	1889.59
47326	.967997	2.64268e-6	12276.8	1892.04
51251	.978596	2.99747e-6	12477.5	1892.04
54847	.990381	3.27357e-6	12675.3	1889.59
58281	1.00171	3.58152e-6	12920.	1891.55
60900	1.01242	3.85038e-6	13124.9	1893.01
64008	1.02339	4.29105e-6	13355.5	1890.08
66382	1.03392	4.64784e-6	13594.2	1892.53
68676	1.04479	5.08078e-6	13838.6	1893.5
70644	1.05635	5.44453e-6	14064.9	1891.55
72776	1.06732	5.85194e-6	14341.3	1891.06
74419	1.07784	6.16975e-6	14577.6	1891.06
76223	1.08847	6.60149e-6	14861.	1892.04
77784	1.09948	7.08273e-6	15124.8	1891.06
79346	1.11034	7.45266e-6	15419.6	1890.57
80663	1.12107	7.86935e-6	15709.6	1892.04
81979	1.13184	8.25386e-6	16009.4	1892.53
83377	1.14275	8.83869e-6	16351.3	1892.53
84531	1.15341	9.46722e-6	16655.9	1891.55
85685	1.16417	1.0335e-5	16991.7	1894.48
86676	1.17499	1.15143e-5	17354.6	1892.53
87667	1.18639	1.32648e-5	17722.9	1892.04
88496	1.19695	1.53373e-5	18106.9	1892.04
89162	1.20782	1.78032e-5	18478.7	1894.48
89745	1.21887	2.09292e-5	18887.2	1894.97
90329	1.2306	2.56765e-5	19370.7	1894.48
90832	1.24363	3.3126e-5	19961.9	1898.39
91172	1.25502	0	0	1897.9
91430	1.26608	0	0	1896.43
91688	1.28	0	0	

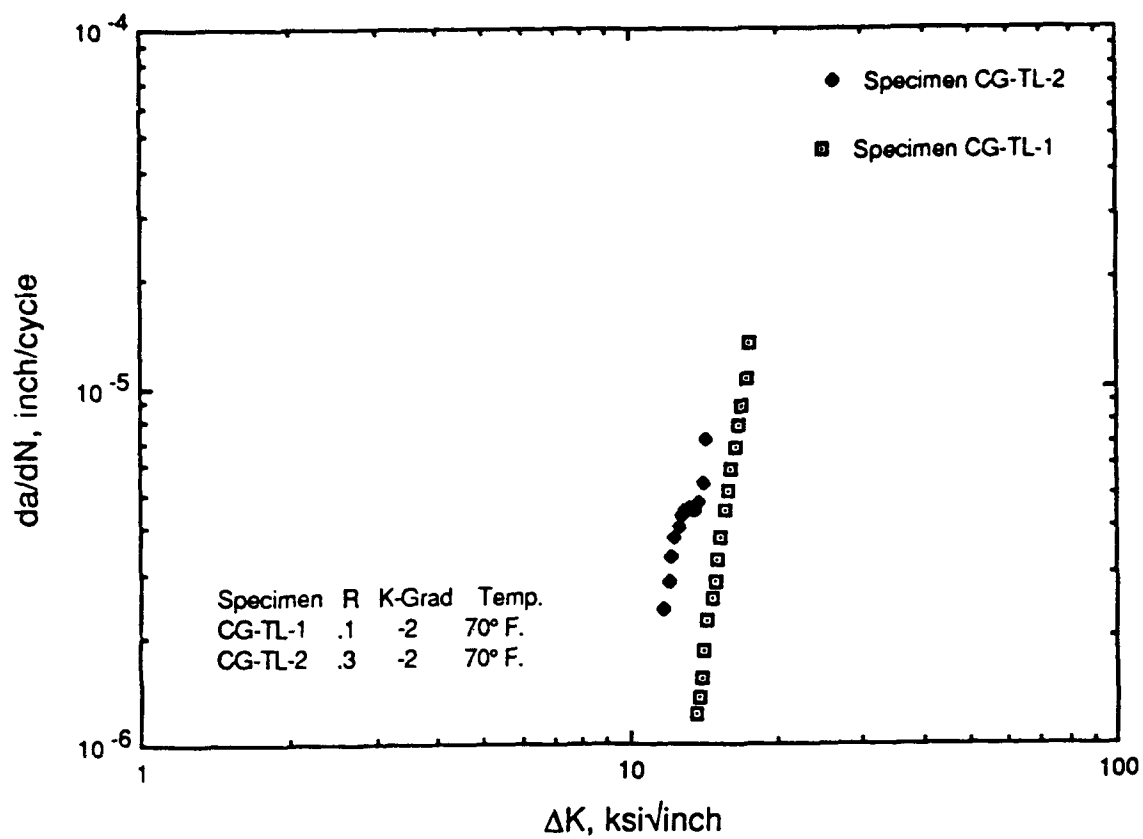


FIGURE F3. Fatigue Crack Growth Rate Data for 8090-T8771 Plate (T-L Orientation).
Martin Marietta.

TABLE F19

Fatigue Crack Growth Rate Data Associated with
Figure F3 (Specimen CG-TL-1)

Tests were performed with the "CGR Crack Growth Program" from Interlaken Version 1.0B.
Strengths are in PSI. Loads in pounds. Dimensions in inches. Temperature in Degrees Fahrenheit. dK in psi sqrt inch.
The crack lengths were corrected based on the final measurements. The data was averaged using the 7 pt. polynomial method.
The precrack Pmax load of 2875 lbs. was 6.8% higher than the initial Pmax test load of 2702 lbs.

Operator:	cpm/ncd
Sample date:	09-24-91
Material:	8090 Al-Li
ID #:	CG-TL-1
Yield Strength:	66850
Modulus of Elast:	11250000
COD Pos:	2
Crack Plane:	T-L
Geometry:	1
Width:	2.0033
Thickness:	1
Half span (MT):	.1
Env:	AIR
Temp:	70
Humidity:	50
Waveform:	1
Test Frequency:	10
Test Type:	1
K Gradient:	-2
Min Load:	270
Max Load:	2700
Test Mode:	1
Data Pt Intvl:	.01
Min Growth Rate:	.00001
Compl Slope:	2
Pts/Cycle:	200
Upper Slope Limit:	85
Lower Slope Limit:	15
No of Slopes Ave:	5
Compliance Cor.:	1.08362
Notch Length:	.8053
Precrack Length:	.9004
Precrack Cycles:	138379
Precrack Max Load:	2874.94
Precrack Min Load:	283.341
#Points:	23

cycle	crack length	dA/dN	dK	Delta Load
76	.900405	0	0	2450.42
12579	.911	0	0	2430.39
23676	.859997	0	0	2430.39
33387	.870441	3.17097e-7	13797.2	2429.9
40247	.879966	7.94854e-7	13771.6	2430.39
47432	.88989	1.53814e-6	14070.7	2427.94
54616	.900886	1.82145e-6	14304.	2429.41
60905	.911076	2.20956e-6	14545.	2429.9
64912	.921716	2.53571e-6	14730.1	2429.9
68511	.931401	2.84312e-6	14937.3	2430.87
72030	.941803	3.26489e-6	15168.5	2430.39
75385	.952745	3.77042e-6	15407.3	2429.41
78412	.963555	4.46241e-6	15685.3	2430.87
80544	.974279	5.08879e-6	15911.2	2430.87
82757	.985828	5.85625e-6	16195.5	2430.87
84644	.997562	6.75067e-6	16470.5	2428.92
86450	1.00981	7.77325e-6	16791.7	2428.92
87848	1.02061	8.72143e-6	17090.7	2429.41
89165	1.03342	1.03738e-5	17412.8	2429.41
90237	1.0442	1.32296e-5	17748.	2431.35
91146	1.05395	0	0	2431.36
91731	1.0653	0	0	2430.87
92151	1.0773	0	0	2431.85

TABLE F20

Fatigue Crack Growth Rate Data Associated with
Figure F3 (Specimen CG-TL-2)

Tests were performed with the "CGR Crack Growth Program" from Interlaken Version 1.0B.
Strengths are in PSI. Loads in pounds. Dimensions in inches. Temperature in Degrees Fahrenheit. dK in psi sqrt inch.
The crack lengths were corrected based on the final measurements. The data was averaged using the 7 pt. polynomial method.
The precrack Pmax load of 2875 lbs. was 6.8% higher than the initial Pmax test load of 2702 lbs.

Operator:	cpm
Sample date:	09-24-91
Material:	8090 Al-Li
ID #:	CG-TL-2
Yield Strength:	66850
Modulus of Elast:	11250000
COD Pos:	2
Crack Plane:	T-L
Geometry:	1
Width:	2.003
Thickness:	1.001
Half span (MT):	.1
Env:	AIR
Temp:	70
Humidity:	50
Waveform:	1
Test Frequency:	10
Test Type:	1
K Gradient:	-2
Min Load:	810
Max Load:	2700
Test Mode:	1
Data Pt Intvl:	.01
Min Growth Rate:	.00001
Compl Slope:	2
Pts/Cycle:	200
Upper Slope Limit:	85
Lower Slope Limit:	15
No of Slopes Ave:	5
Compliance Cor.:	1.07341
Notch Length:	.8035
Precrack Length:	.9215
Precrack Cycles:	123206
Precrack Max Load:	2874.94
Precrack Min Load:	862.237
#Points:	19

cycle	crack length	dA/dN	dK	Delta Load
76	.909805	0	0	1962.38
10687	.920906	0	0	1889.11
17714	.931758	0	0	1891.55
22701	.94231	2.37086e-6	11807.6	1891.55
27281	.953011	2.85092e-6	12007.1	1892.04
30963	.964681	3.3215e-6	12208.7	1893.01
34320	.97642	3.74497e-6	12420.5	1892.53
37024	.986889	4.03343e-6	12628.5	1893.01
39483	.997977	4.28854e-6	12811.9	1890.57
42187	1.00979	4.45745e-6	13055.4	1890.57
44645	1.02063	4.52734e-6	13280.8	1889.59
46697	1.031	4.49661e-6	13493.4	1891.55
49075	1.04121	4.52118e-6	13715.1	1890.08
51372	1.05164	4.71378e-6	13954.5	1892.53
53828	1.06194	5.30214e-6	14194.	1890.57
56122	1.0731	7.0252e-6	14493.7	1891.55
57764	1.08461	0	0	1892.04
58917	1.09475	0	0	1891.06
59582	1.107	0	0	1894.48

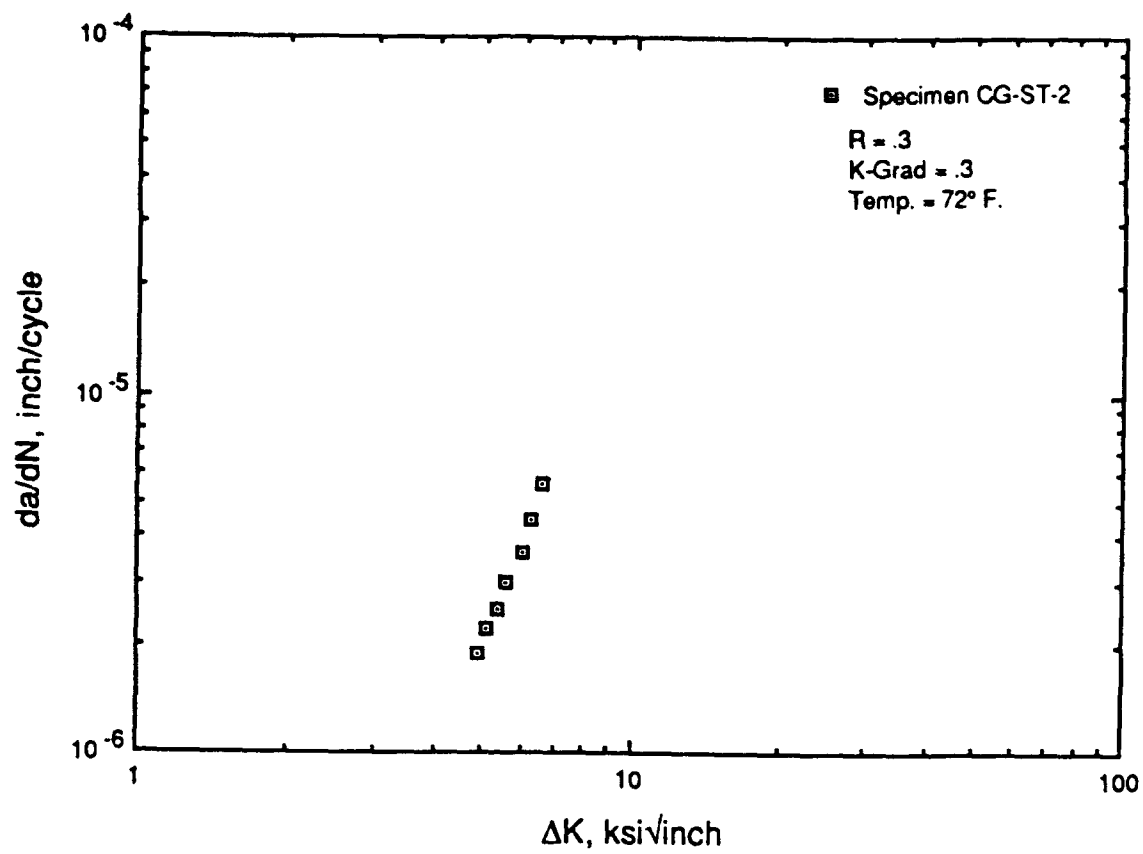


FIGURE F4. Fatigue Crack Growth Rate Data for 8090-T8771 Plate (S-T Orientation).
Martin Marietta.

TABLE F21

Fatigue Crack Growth Rate Data Associated with
Figure F4 (Specimen CG-ST-2)

Tests were performed with the "CGR Crack Growth Program" from Interlaken Version 1.0B.
Strengths are in PSI. Loads in pounds. Dimensions in inches. Temperature in Degrees Fahrenheit. dK in psi sqrt inch.
The crack lengths were corrected based on the final measurements. The data was averaged using the 7 pt. polynomial method.

Operator:	Chris Miller
Sample date:	08-18-91
Material:	8090-T8771
ID #:	CG-ST-2
Yield Strength:	71000
Modulus of Elast:	11200000
COD Pos:	2
Crack Plane:	ST
Geometry:	1
Width:	1.4035
Thickness:	.701
Half span (MT):	.1
Env:	Air
Temp:	72
Humidity:	51
Waveform:	1
Test Frequency:	10
Test Type:	1
K Gradient:	-2
Min Load:	150
Max Load:	500
Test Mode:	1
Data Pt Intvl:	.01
Min Growth Rate:	.000001
Compl Slope:	3
Pts/Cycle:	200
Upper Slope Limit:	85
Lower Slope Limit:	15
No of Slopes Ave:	5
Compliance Cor.:	.985189
Notch Length:	.563
Precrack Length:	.72
Precrack Cycles:	118121
Precrack Max Load:	500
Precrack Min Load:	150
#Points:	13

cycle	crack length	dA/dN	dK	Delta Load
119	.719281	0	0	355.642
16867	.736786	0	0	354.079
29310	.754402	0	0	355.642
39292	.772179	1.86994e-6	4866.63	355.642
48502	.790093	2.15482e-6	5093.44	355.642
56445	.80808	2.47499e-6	5354.75	357.206
63860	.825916	2.96648e-6	5644.28	358.183
69901	.843877	3.64302e-6	5973.53	360.528
74887	.861517	4.52111e-6	6328.71	362.286
78421	.879265	5.58259e-6	6617.91	361.114
81529	.8968	0	0	362.677
84214	.914419	0	0	365.217
85986	.932	0	0	368.539

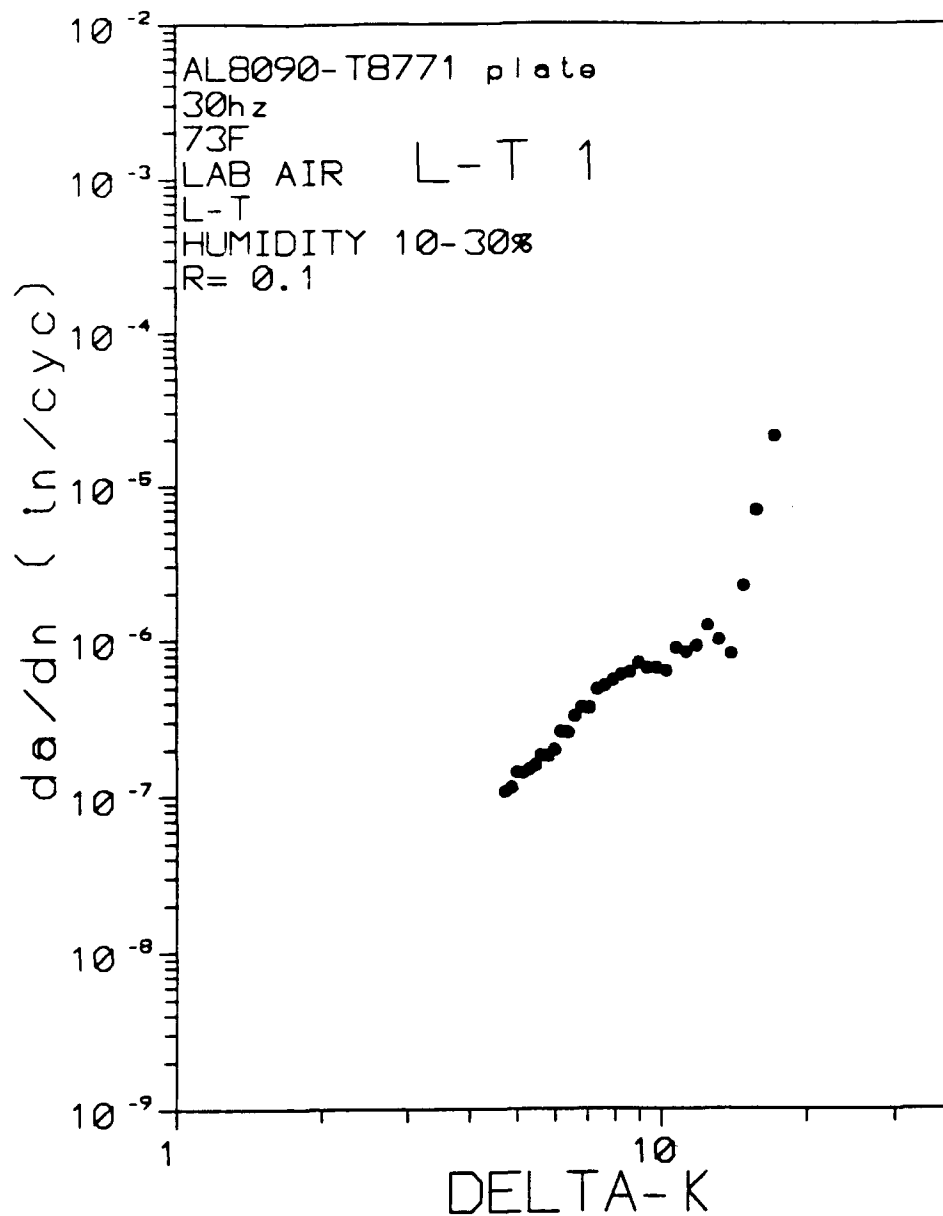


FIGURE F5. Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation and R=0.1).
 Air Force.

TABLE F22

Fatigue Crack Growth Rate Data Associated with
Figure F5

MATERIAL: ALUMINUM
 ALLOY: 8090
 CONDITION/HT: T8771
 FORM: 1.75 IN. PLATE
 .2% YIELD STRENGTH (KSI): 68
 ULT. STRENGTH (KSI): 77
 MODULUS: 11.0
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 SPECIMEN I.D. LT1
 SPECIMEN WIDTH: 2.005
 SPECIMEN THK.: .249

MAX. LOAD (LBS): 222
 MIN. LOAD (LBS): 22
 STRESS RATIO: 0.1
 TEST FREQUENCY Hz: 30
 CYCLIC WAVE FORM: SINE
 TEST PROCEDURE: K-INCREASING
 ENVIRONMENT: LAB AIR
 TEST TEMPERATURE F: 73F
 RELATIVE HUMIDITY: 10-30%
 MEASUREMENT INTERVAL (IN.): .020
 CRACK MEASUREMENT METHOD: COMPLIANCE

a (in)	kilocycles	da/dN (in/cyc)	Del K (KSI-in ^{0.5})
0.566	32.00	3.17E-07	6.52
0.576	77.70	2.21E-07	6.08
0.587	132.50	1.87E-07	5.71
0.597	191.60	1.71E-07	5.43
0.607	263.20	1.41E-07	5.10
0.617	325.60	1.64E-07	4.77
0.627	399.30	1.39E-07	4.47
0.637	478.50	1.28E-07	4.19
0.647	584.40	9.65E-08	3.92
0.658	695.80	9.08E-08	3.76
0.668	845.20	6.76E-08	3.52
0.678	1079.10	4.31E-08	3.32
0.688	1456.30	2.68E-08	3.10
0.710	2807.30	6.65E-08	3.62
0.730	2988.00	1.11E-07	3.69
0.750	3160.70	1.16E-07	3.79
0.770	3298.50	1.45E-07	3.89
0.790	3439.10	1.44E-07	3.98
0.810	3571.20	1.52E-07	4.09
0.830	3694.10	1.63E-07	4.19
0.850	3801.40	1.87E-07	4.30
0.871	3910.60	1.85E-07	4.42
0.891	4009.70	2.02E-07	4.54
0.911	4086.10	2.62E-07	4.65
0.931	4162.90	2.61E-07	4.78
0.951	4224.10	3.32E-07	4.89
0.971	4276.80	3.80E-07	5.06
0.991	4329.70	3.79E-07	5.19
1.011	4370.10	4.96E-07	5.33
1.031	4406.40	5.26E-07	5.46
1.051	4443.50	5.72E-07	5.62
1.072	4476.10	6.19E-07	5.98
1.092	4507.40	6.40E-07	6.12
1.112	4534.90	7.30E-07	6.29
1.132	4564.50	6.77E-07	6.42
1.152	4594.20	6.75E-07	6.79
1.172	4625.50	6.44E-07	6.94
1.192	4647.80	9.07E-07	7.13
1.212	4671.50	8.51E-07	7.64
1.233	4693.10	9.31E-07	7.88
1.253	4709.20	1.26E-06	8.08
1.273	4729.20	1.03E-06	8.53
1.293	4753.40	8.29E-07	8.84
1.314	4762.30	2.27E-06	9.43
1.334	4765.20	6.87E-06	9.76
1.368	4766.80	2.25E-05	9.99

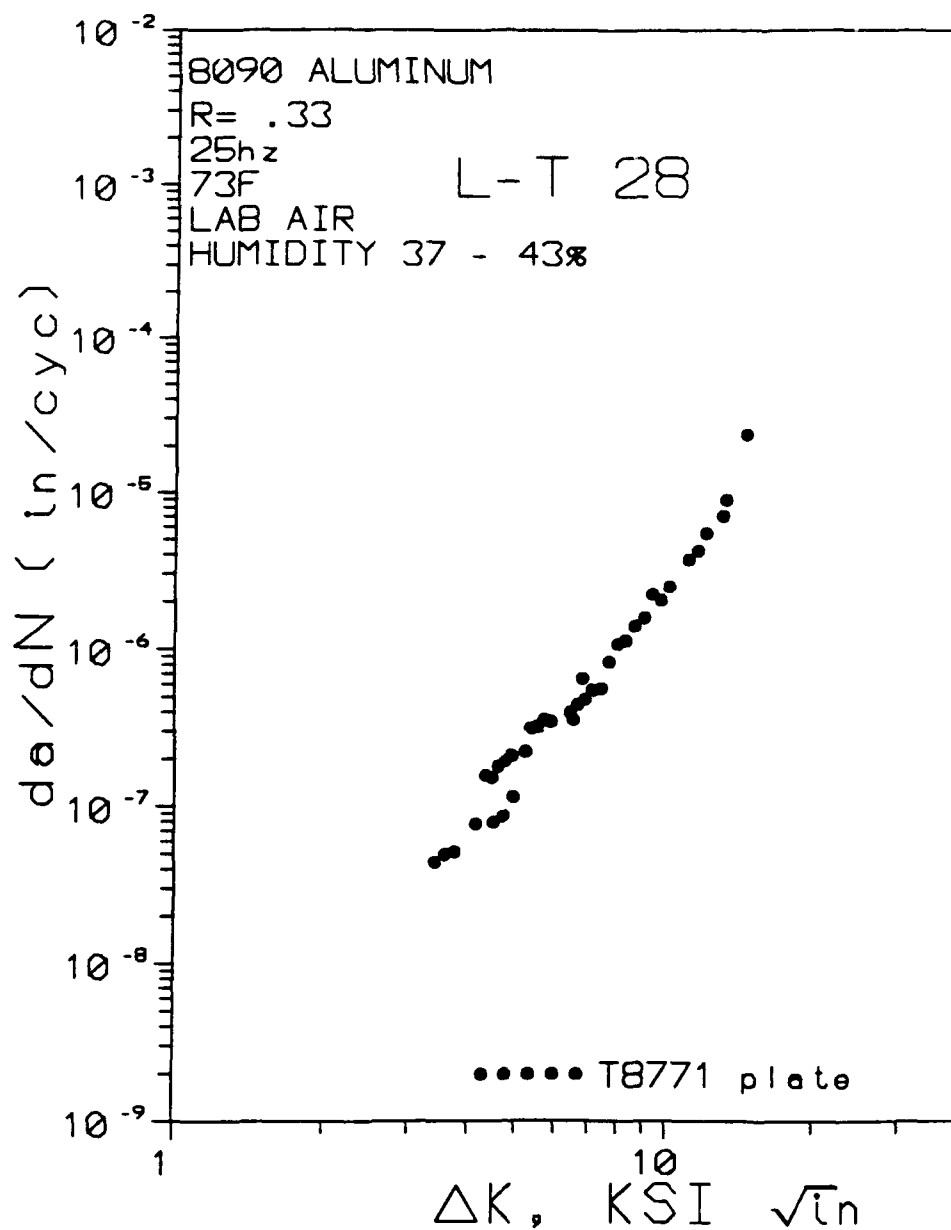


FIGURE F6. Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation and R=0.33). Air Force.

TABLE F23

Fatigue Crack Growth Rate Data Associated with
Figure F6

MATERIAL: ALUMINUM
 ALLOY: 8090
 CONDITION/HT: T8771
 FORM: 1.75 IN. PLATE
 2% YIELD STRENGTH (KSI): 68
 ULT. STRENGTH (KSI): 77
 MODULUS: 11.0
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 SPECIMEN I.D.: LT28
 SPECIMEN WIDTH: 2.003
 SPECIMEN THK.: .248

MAX. LOAD (LBS): 289
 MIN. LOAD (LBS): 95
 STRESS RATIO: 0.33
 TEST FREQUENCY Hz: 15
 CYCLIC WAVE FORM: SINE
 TEST PROCEDURE: K-INCREASING
 ENVIRONMENT: LAB AIR
 TEST TEMPERATURE F: 74
 RELATIVE HUMIDITY: 36-44%
 MEASUREMENT INTERVAL (IN.): .020
 CRACK MEASUREMENT METHOD: COMPLIANCE

a (in)	cycles	da/dN (in/cycle)	Del K (KSI-in ^{0.5})
0.651	1081720.00	7.74E-08	4.13
0.672	1487480.00	5.17E-08	3.74
0.683	1703550.00	4.97E-08	3.57
0.693	1932910.00	4.43E-08	3.40
0.894	3297950.00	1.57E-07	4.33
0.914	3429750.00	1.52E-07	4.46
0.935	3544860.00	1.80E-07	4.60
0.956	3655400.00	1.92E-07	4.74
0.977	3754060.00	2.10E-07	4.90
1.018	3923630.00	2.22E-07	5.22
1.038	3989040.00	3.13E-07	5.36
1.058	4051680.00	3.22E-07	5.53
1.078	4108720.00	3.55E-07	5.70
1.099	4168270.00	3.44E-07	5.88
1.119	4219330.00	3.95E-07	6.43
1.139	4264410.00	4.44E-07	6.65
1.159	4306060.00	4.82E-07	6.89
1.179	4342560.00	5.50E-07	7.11
1.199	4378020.00	5.66E-07	7.41
1.220	4402510.00	8.35E-07	7.68
1.240	4421030.00	1.08E-06	7.99
1.260	4438650.00	1.14E-06	8.28
1.281	4453290.00	1.41E-06	8.61
1.301	4466100.00	1.59E-06	9.00
1.321	4475020.00	2.25E-06	9.35
1.341	4484810.00	2.07E-06	9.72
1.362	4493080.00	2.50E-06	10.12
1.383	4498580.00	3.76E-06	11.04
1.403	4503380.00	4.29E-06	11.52
1.423	4507010.00	5.56E-06	11.96
1.444	4509900.00	7.16E-06	12.94
1.466	4512350.00	9.10E-06	13.13
1.489	4513300.00	2.41E-05	14.43

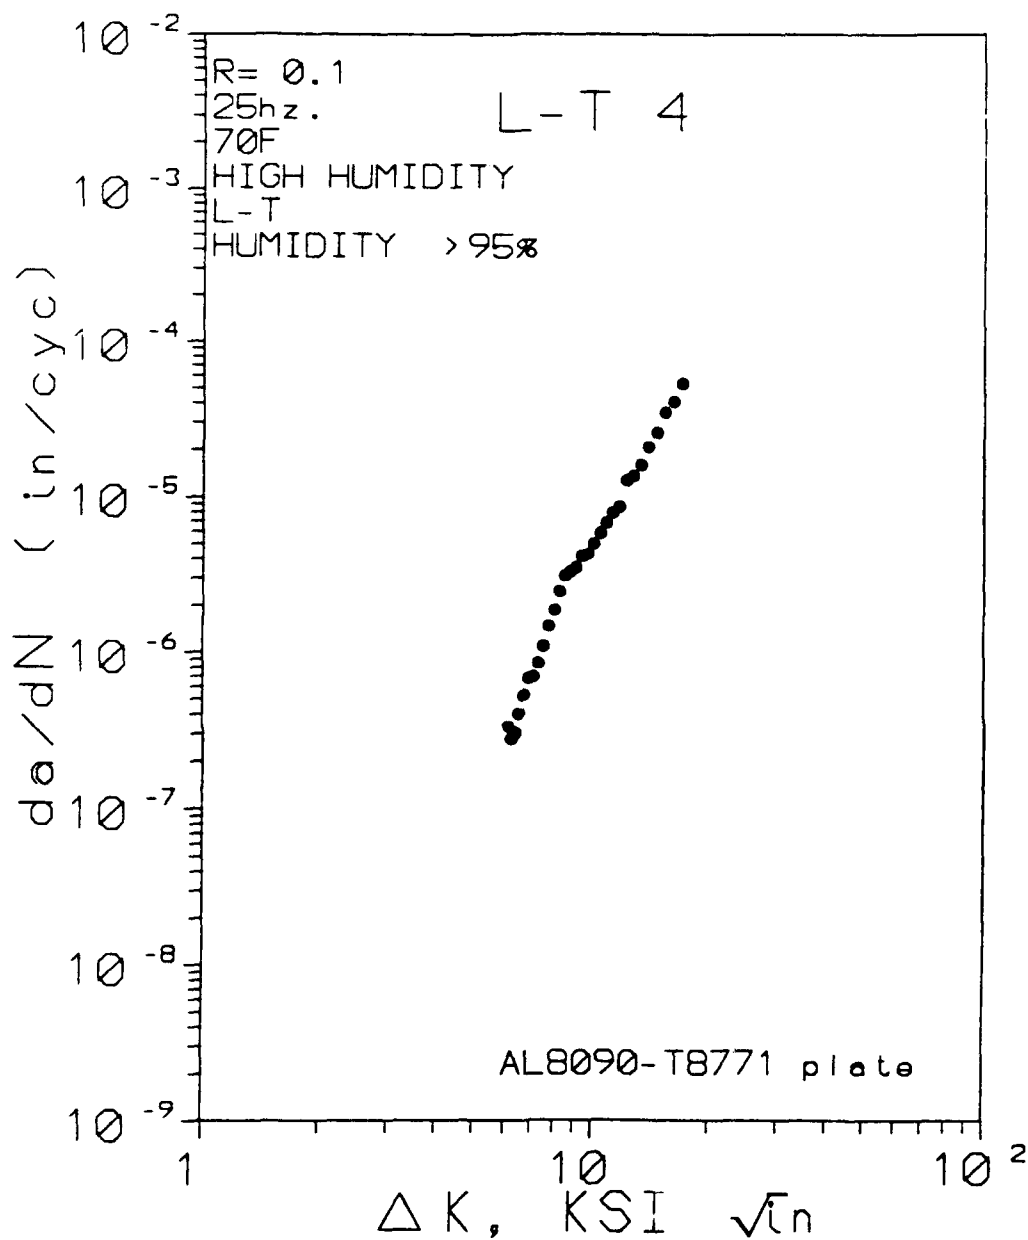


FIGURE F7. Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation and $R=0.1$ and High Humidity). Air Force.

TABLE F24

Fatigue Crack Growth Rate Data Associated with
Figure F7

MATERIAL: ALUMINUM
 ALLOY: 8090
 CONDITION/HT: T8771
 FORM: 1.75 IN. PLATE
 .2% YIELD STRENGTH (KSI): 68
 ULT. STRENGTH (KSI): 77
 MODULUS: 11.0
 SPECIMEN TYPE: CT
 ORIENTATION: L-T
 SPECIMEN I.D. LT4
 SPECIMEN WIDTH: 2.004
 SPECIMEN THK.: .250

MAX. LOAD (LBS): 329
 MIN. LOAD (LBS): 33
 STRESS RATIO: 0.1
 TEST FREQUENCY Hz: 5
 CYCLIC WAVE FORM: SINE
 TEST PROCEDURE: K-INCREASING
 ENVIRONMENT: HIGH HUMIDITY
 TEST TEMPERATURE F: 70F
 RELATIVE HUMIDITY: >95%
 MEASUREMENT INTERVAL (IN): .020
 CRACK MEASUREMENT METHOD: COMPLIANCE

a (in)	N cycles	da/dN (in/cyc)	Del K (KSI-in ^{0.5})
0.806	790683.00	3.32E-07	6.13
0.816	827331.00	2.80E-07	6.21
0.836	893108.00	3.05E-07	6.34
0.856	943212.00	4.04E-07	6.51
0.876	981320.00	5.27E-07	6.69
0.896	1011050.00	6.78E-07	6.88
0.917	1040110.00	6.98E-07	7.07
0.937	1064010.00	8.52E-07	7.28
0.957	1082430.00	1.09E-06	7.50
0.978	1096220.00	1.48E-06	7.73
0.998	1106990.00	1.87E-06	7.97
1.018	1115150.00	2.47E-06	8.22
1.038	1121650.00	3.12E-06	8.49
1.058	1127710.00	3.31E-06	8.75
1.079	1133480.00	3.52E-06	9.05
1.098	1138400.00	4.18E-06	9.37
1.119	1143100.00	4.28E-06	9.70
1.139	1147140.00	4.98E-06	10.04
1.160	1150590.00	5.85E-06	10.44
1.180	1153800.00	6.82E-06	10.83
1.200	1156140.00	7.94E-06	11.26
1.220	1158450.00	8.67E-06	11.71
1.240	1160020.00	1.28E-05	12.20
1.261	1161490.00	1.37E-05	12.71
1.281	1162770.00	1.61E-05	13.28
1.302	1163760.00	2.11E-05	13.89
1.323	1164570.00	2.60E-05	14.57
1.344	1165150.00	3.52E-05	15.27
1.365	1165660.00	4.13E-05	16.05
1.386	1166060.00	5.42E-05	16.93

TABLE F25

Fatigue Crack Growth Rate Data Associated with
Figure F8

MATERIAL: ALUMINUM	MAX. LOAD (LBS): 249
ALLOY: 8090	MIN. LOAD (LBS): 82
CONDITION/HT: T8771	STRESS RATIO: 0.33
FORM: 1.75 IN. PLATE	TEST FREQUENCY Hz: 15
.2% YIELD STRENGTH (KSI): 68	CYCLIC WAVE FORM: SINE
ULT. STRENGTH (KSI): 77	TEST PROCEDURE: K-INCREASING
MODULUS: 11.0	ENVIRONMENT: HIGH HUMIDITY
SPECIMEN TYPE: CT	TEST TEMPERATURE F: 78
ORIENTATION: L-T	RELATIVE HUMIDITY: >95%
SPECIMEN I.D. LT27	MEASUREMENT INTERVAL (IN.): .020
SPECIMEN WIDTH: 2.004	CRACK MEASUREMENT METHOD: COMPLIANCE
SPECIMEN THK.: .248	

a (in)	cycles	da/dN (in/cyc)	Del K (KSI-in ^{0.5})
0.624	132833.00	2.79E-07	4.87
0.634	177724.00	2.26E-07	4.60
0.644	232883.00	1.83E-07	4.40
0.655	313581.00	1.37E-07	4.11
0.666	397311.00	1.27E-07	3.85
0.676	508427.00	9.35E-08	3.62
0.686	641947.00	7.51E-08	3.41
0.696	760683.00	6.59E-08	3.27
0.707	983856.00	4.98E-08	3.05
0.729	1320890.00	1.11E-07	3.17
0.739	1414070.00	1.11E-07	3.21
0.750	1514790.00	1.09E-07	3.25
0.760	1601580.00	1.15E-07	3.30
0.780	1748260.00	1.37E-07	3.35
0.800	1889030.00	1.43E-07	3.44
0.821	2034240.00	1.42E-07	3.54
0.842	2179440.00	1.46E-07	3.64
0.862	2325920.00	1.38E-07	3.75
0.882	2467230.00	1.42E-07	3.84
0.902	2590630.00	1.62E-07	3.95
0.923	2714700.00	1.63E-07	4.08
0.943	2819900.00	1.91E-07	4.18
0.963	2918330.00	2.08E-07	4.31
0.983	3012330.00	2.17E-07	4.45
1.004	3101480.00	2.34E-07	4.59
1.026	3181830.00	2.67E-07	4.75
1.046	3254410.00	2.76E-07	4.90
1.066	3315480.00	3.30E-07	5.07
1.086	3378050.00	3.21E-07	5.24
1.106	3436150.00	3.52E-07	5.42
1.127	3485720.00	4.13E-07	5.61
1.147	3530230.00	4.58E-07	5.82
1.168	3562070.00	6.47E-07	6.04
1.188	3591080.00	7.04E-07	6.28
1.208	3616030.00	8.06E-07	6.53
1.228	3635920.00	1.01E-06	6.79
1.249	3650250.00	1.42E-06	7.03
1.269	3661430.00	1.83E-06	7.34
1.290	3671310.00	2.06E-06	7.64
1.310	3680800.00	2.18E-06	7.98
1.331	3688050.00	2.79E-06	8.34
1.352	3694990.00	3.05E-06	8.70
1.372	3700960.00	3.37E-06	9.10
1.392	3706060.00	4.01E-06	9.52
1.414	3710530.00	4.97E-06	9.97
1.435	3714260.00	5.59E-06	10.47
1.457	3717390.00	6.96E-06	10.95
1.479	3719930.00	8.65E-06	11.45
1.502	3722000.00	1.13E-05	11.99
1.531	3723200.00	2.41E-05	12.61

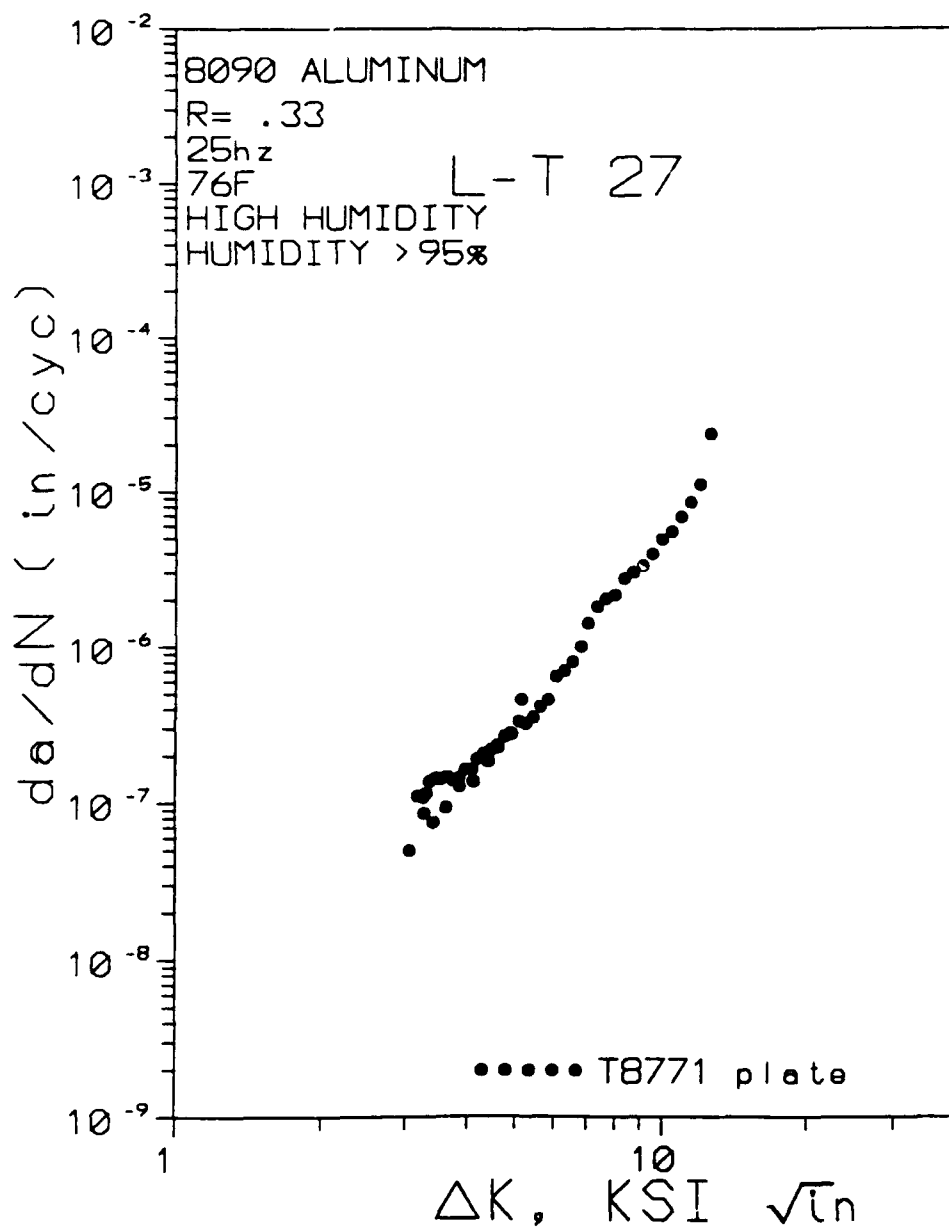


FIGURE F8. Fatigue Crack Growth Rate Data for 8090-T8771 Plate (L-T Orientation and R=0.33 and High Humidity). Air Force.

MINI-TWIST 16.9 KSI

AL8090 PL-2

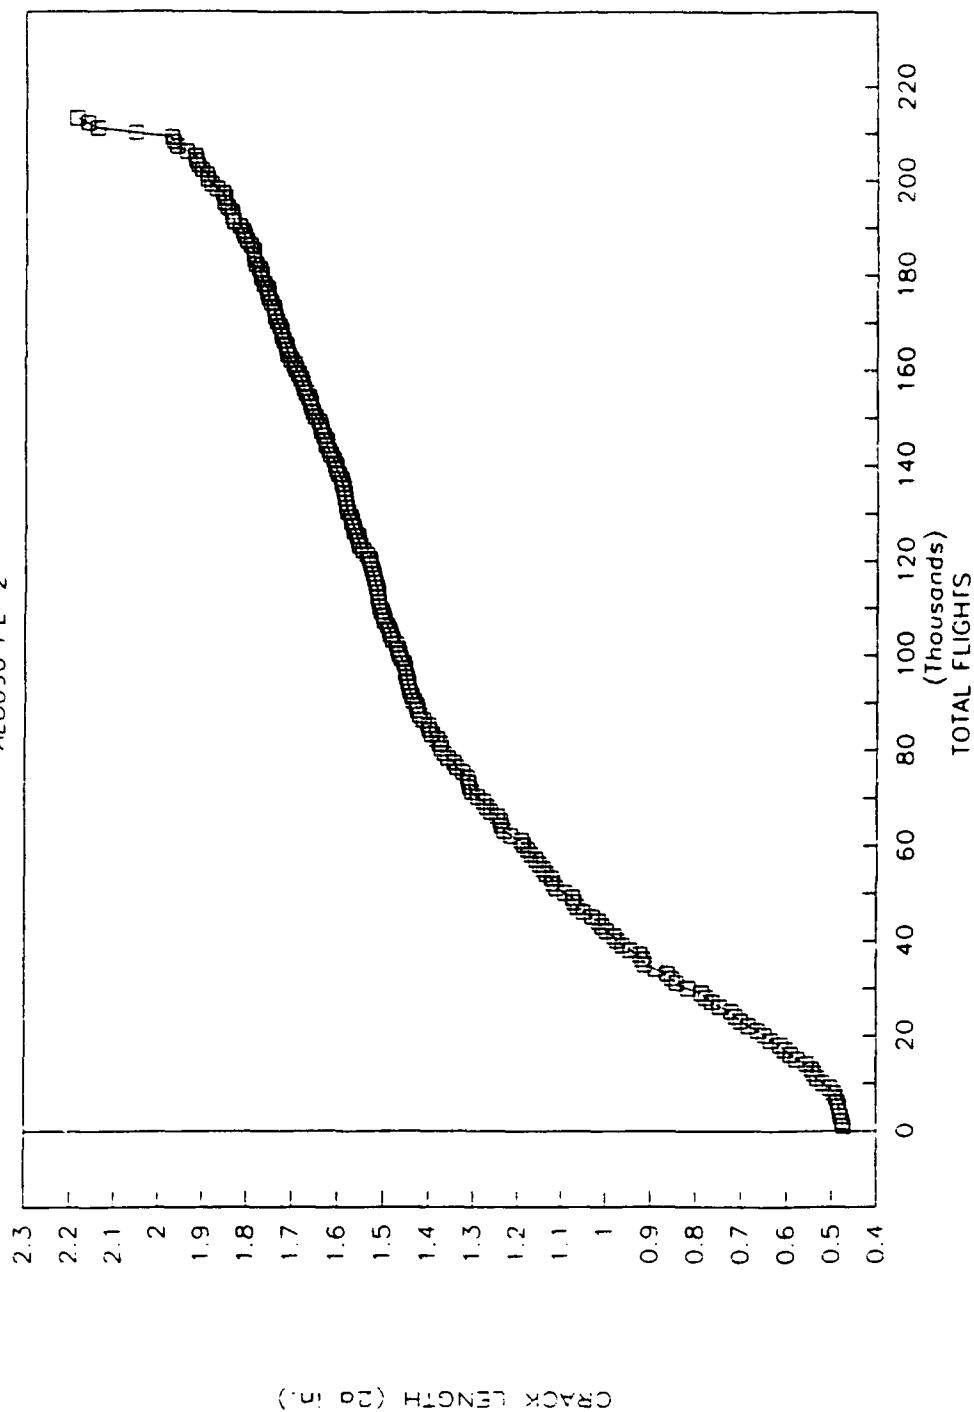


FIGURE F9. Mini-TWIST Spectrum Crack Length vs Flights Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 16.9 Ksi). Air Force.

MINI-TWIST 16.9 KSI

AL8090 PL-2

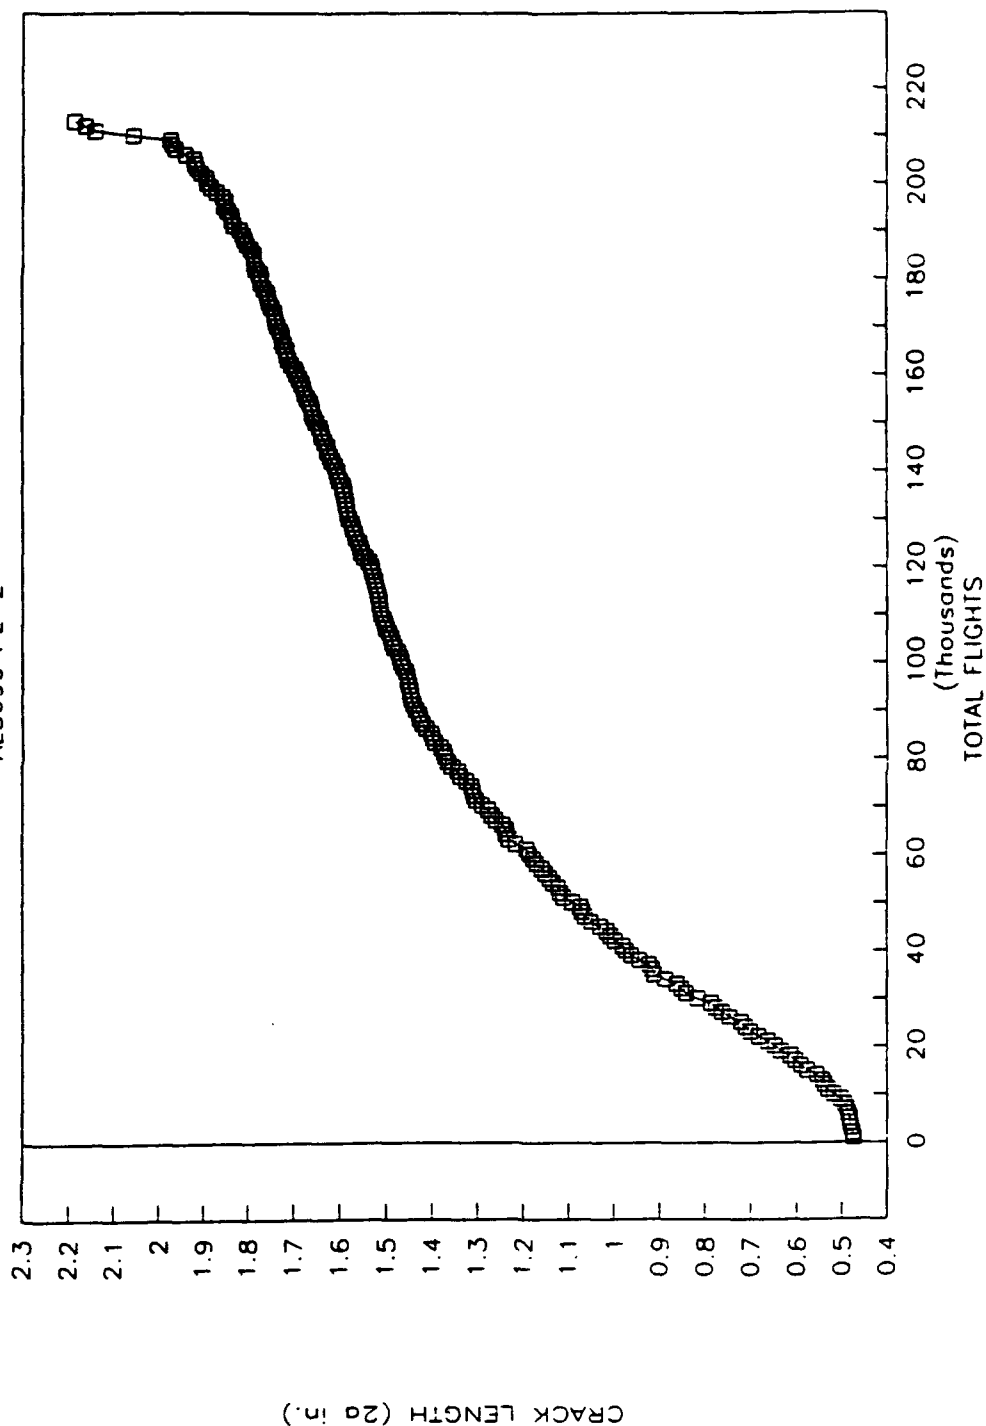


FIGURE F9. Mini-TWIST Spectrum Crack Length vs Flights Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 16.9 Ksi). Air Force.

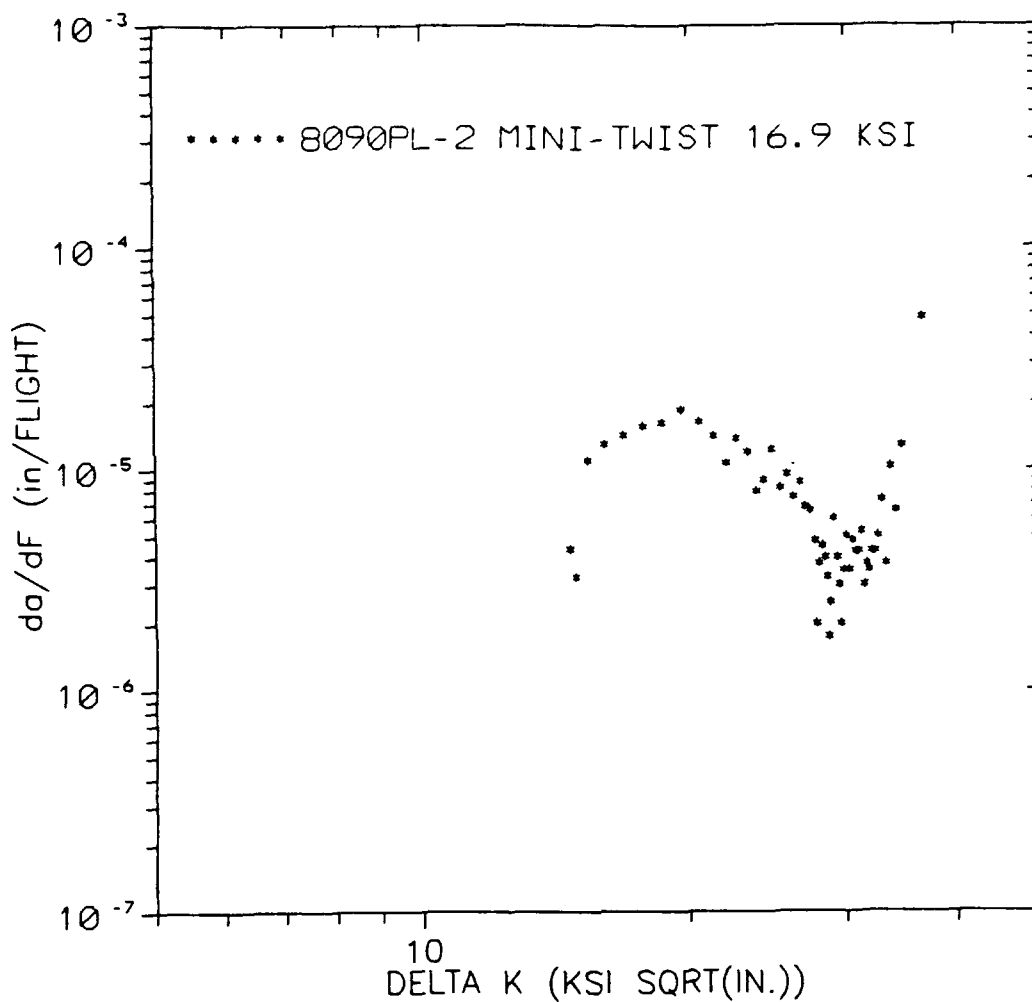


FIGURE F10. Mini-TWIST Spectrum Crack Growth Rate vs Delta K Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 16.9 KSU). Air Force.

8090PL1

FALSTAFF 20 KSI

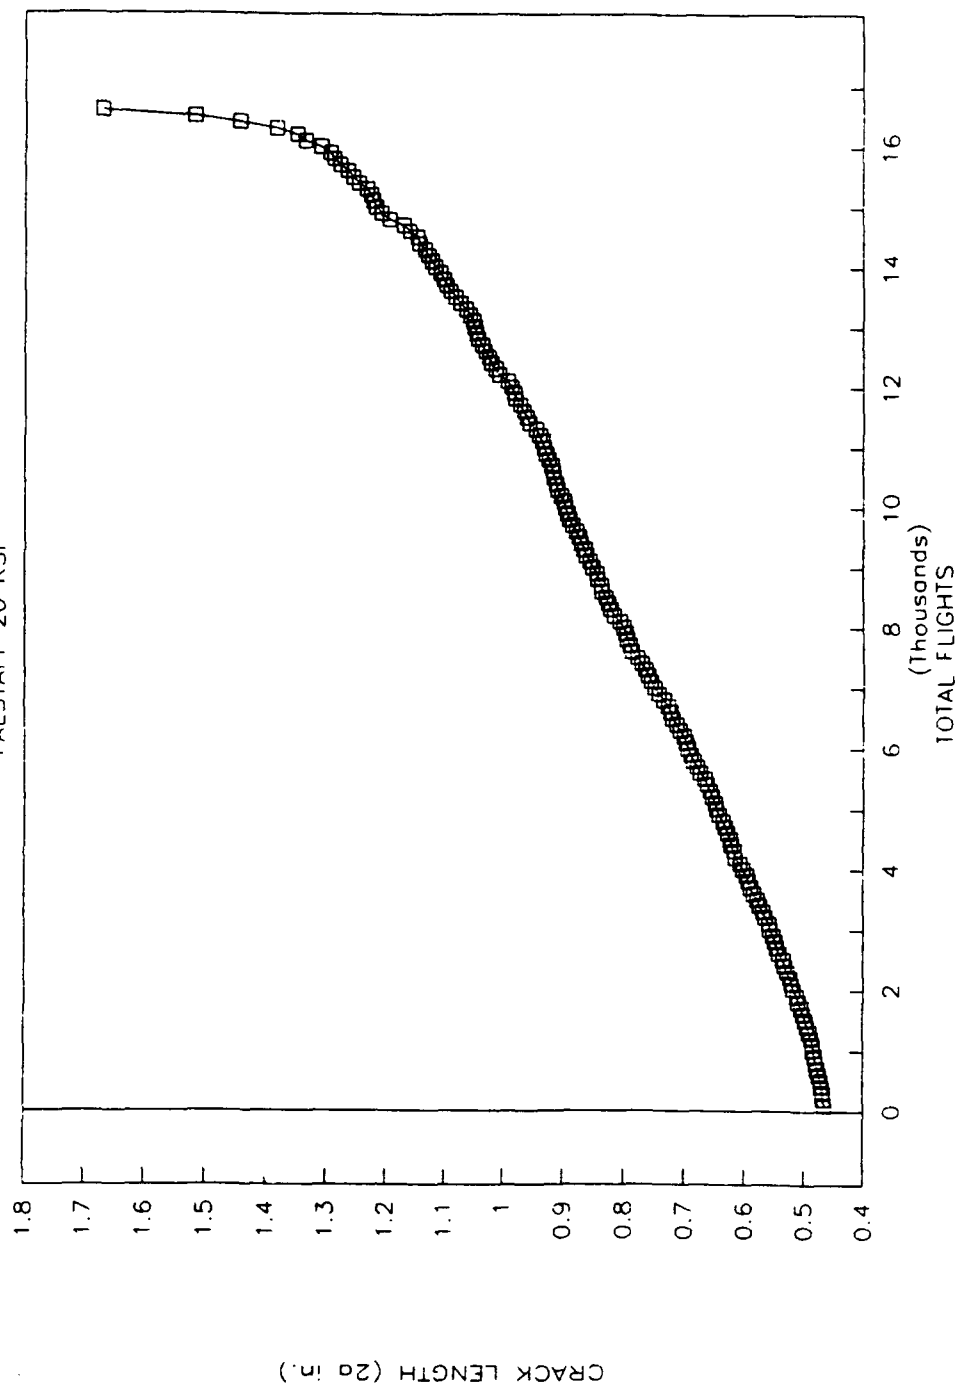


FIGURE F11. FALSTAFF Spectrum Crack Length vs Total Flights Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 20 Ksi). Air Force.

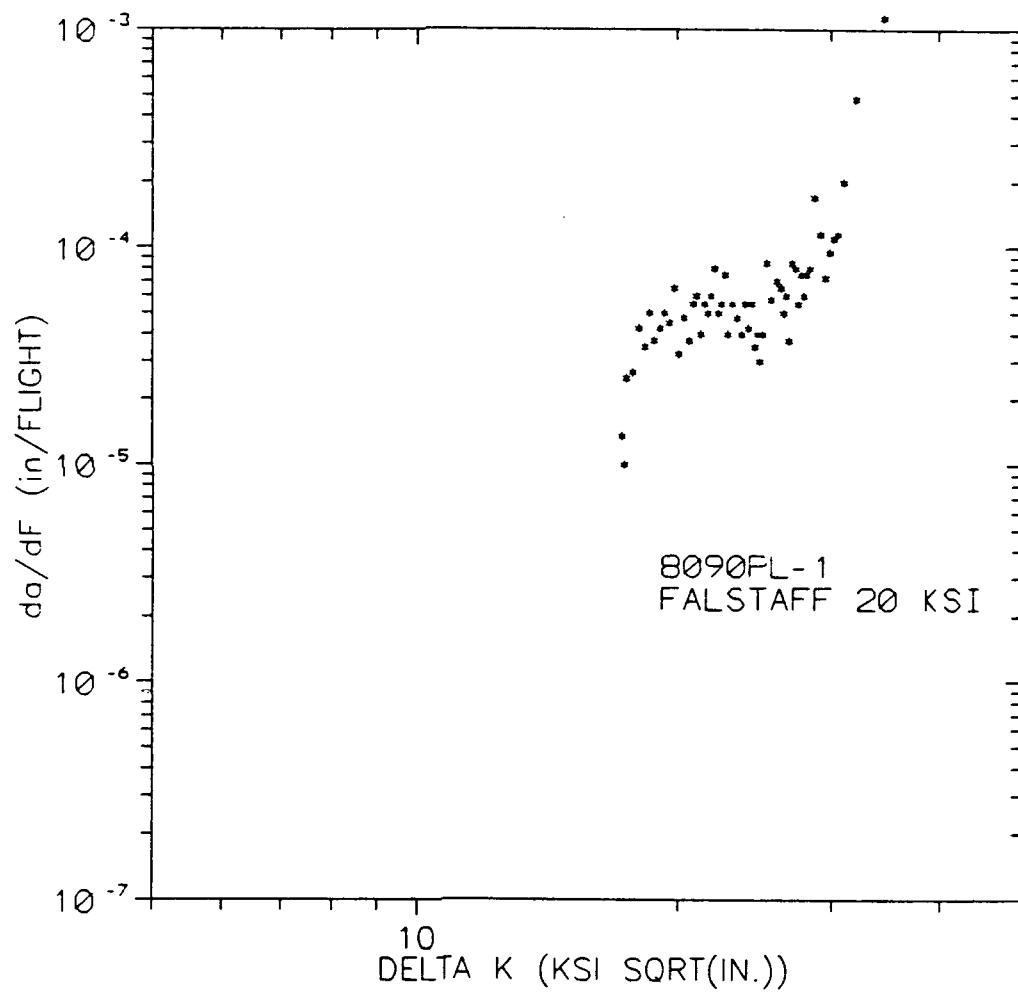


FIGURE F12. FALSTAFF Spectrum Crack Growth Rate vs Delta K Data for 8090-T8771 Plate (L-T Orientation, Room Temperature, Lab Air and Maximum Stress = 20 Ksi).
Air Force.