

AD-A273 626



TION PAGE

Form Approved
OMB No. 0704-0188

1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering information, and reviewing comments regarding this burden estimate or any other aspect of this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE 29 NOV 93	3. REPORT TYPE AND DATES COVERED technical; 01JUN93 to 31MAY94	
4. TITLE AND SUBTITLE Dipolar Relaxation in a Second-Order Nonlinear Optical Interpenetrating Polymer Network			5. FUNDING NUMBERS C: N00014-90-J-1148	
6. AUTHOR(S) J. I. Chen, S. Marturunkakul, L. Li, R. J. Jeng, J. Kumar, S. K. Tripathy			R&T Code: 4132016 Dr. JoAnn Milliken	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of Massachusetts Lowell Department of Chemistry 1 University Avenue Lowell, MA 01854			8. PERFORMING ORGANIZATION REPORT NUMBER 1148-94-02	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research-Chemistry Division Code 1113 Department of the Navy Arlington, Virginia 22217-5000			10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION / AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 Words) The nature of the relaxation process of the poled order in an interpenetrating polymer network (IPN) system is found to be fundamentally different from that of a guest/host system. The IPN (T _g = 176 °C) consists of a nonlinear optical (NLO) active epoxy-based polymer network and an NLO active phenoxy-silicon polymer network. The decay behavior of the second-order nonlinearity of this IPN was investigated in the range from 110 to 170 °C. The stability of this IPN is superior to those of classic guest/host polymers as indicated by longer relaxation times at temperatures from 110 to 130 °C. The relaxation process of the IPN system follows Arrhenius type behavior at temperatures ranging from 140 to 170 °C. The IPN system provides a new approach to processing for stabilization of the second-order nonlinear optical properties.				
14. SUBJECT TERMS relaxation, interpenetrating polymer network, nonlinear optical, Arrhenius			15. NUMBER OF PAGES 14	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

DTIC
S ELECTE
DEC 08 1993
A

Standard Form 298 (Rev. 2-89)
Prescribed by ANSI Std. Z39-18
298-102

93-29868



93 12 7 063

6

OFFICE OF NAVAL RESEARCH

GRANT N00014-90-J-1148

R&T Code 4132016

Scientific Officer: Dr. JoAnn Milliken

Technical Report No. 94-02

**Dipolar Relaxation in a Second-Order Nonlinear
Optical Interpenetrating Polymer Network**

by

**J. I. Chen, S. Marturunkakul
L. Li, R. J. Jeng, J. Kumar, S. K. Tripathy**

Submitted to Macromolecules

**University of Massachusetts Lowell
Department of Chemistry
Lowell, Massachusetts**

November 29, 1993

DTIC QUALITY INSPECTED 3

Accession For	
NTIS CRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

**Reproduction in whole or in part is permitted for any purpose of the
United States Government.**

**This document has been approved for public release and sale; its
distribution is unlimited.**

Dipolar Relaxation in a Second-Order Nonlinear Optical Interpenetrating Polymer Network

J. I. Chen, S. Marturunkakul, L. Li¹, R. J. Jeng, J. Kumar¹, and S. K. Tripathy*,
Center for Advanced Materials, Departments of Chemistry and Physics¹,
University of Massachusetts Lowell, Lowell, MA 01854, USA

Abstract

The nature of the relaxation process of the poled order in an interpenetrating polymer network (IPN) system is found to be fundamentally different from that of a guest/host system. The IPN ($T_g = 176$ °C) consists of a nonlinear optical (NLO) active epoxy-based polymer network and an NLO active phenoxy-silicon polymer network. The decay behavior of the second-order nonlinearity of this IPN was investigated in the range from 110 to 170 °C. The stability of this IPN is superior to those of classic guest/host polymers as indicated by longer relaxation times at temperatures from 110 to 130 °C. The relaxation process of the IPN system follows Arrhenius type behavior at temperatures ranging from 140 to 170 °C. The IPN system provides a new approach to processing for stabilization of the second-order nonlinear optical properties.

Dipolar Relaxation in a Second-Order Nonlinear Optical Interpenetrating Polymer Network

J. I. Chen, S. Marturunkakul, L. Li¹, R. J. Jeng, J. Kumar¹, and S. K. Tripathy*, Center for Advanced Materials, Departments of Chemistry and Physics¹, University of Massachusetts Lowell, Lowell, MA 01854, USA

Second-order nonlinear optical (NLO) materials are of much interest for applications such as electro-optic modulation and frequency conversion.¹⁻³ Polymeric second-order NLO materials have been studied extensively in recent years⁴⁻⁹ due to their low dielectric constant, large nonlinearity, and ease of processability compared to inorganic NLO materials. In these polymeric systems, the noncentrosymmetric alignment of NLO chromophores achieved by the poling technique³ is responsible for the NLO properties. However, the decay of the poled order as the material is subjected to high temperatures is still an outstanding problem. In order to use these materials in practical applications, the long term NLO stability at temperatures up to 100 °C with spikes to higher temperatures is required during device fabrication and operation. Therefore, an understanding of this decay process is the key to the development of stable polymeric NLO materials.

The relaxation of aligned NLO chromophores is often characterized by monitoring the decay of second harmonic (SH) generation as a function of time at different temperatures.^{10,11} In a typical guest/host system where chromophores are dispersed in an amorphous polymer, Stähelin et al. were able to fit the temporal relaxation to a Kohlrausch-Williams-Watts (KWW) equation establishing that the decay of the dipole alignment is

explained by a single relaxation phenomenon.¹¹ A fit of the relaxation times to the Williams-Landel-Ferry (WLF) equation pointed out that relaxation of the second-order NLO properties is mainly related to the glass transition temperature (T_g) of the media. Thus high T_g polymers are sought for stability at elevated temperatures. In other reports,^{4,6,7} increased crosslinking has been used as a vehicle to enhance the NLO stability. Crosslinking networks reduce the mobility of the polymer chains which further prevent the aligned NLO chromophores from relaxing to a random orientation. Improved stability of the nonlinear response was established in a system with higher crosslinking density.⁷ However, polymers which possess high T_g as well as high crosslinking density still exhibit slow decay of the NLO properties at elevated temperatures. Although qualitatively the relaxation behavior of crosslinked systems at elevated temperatures seems similar to guest/host systems, a detail experimental comparison of the relaxation behavior of the two systems has not been reported.

The important issues we would like to address in this report are the role of crosslinking in the stabilization of the NLO properties and the differences in the relaxation behaviors between the crosslinked network and a classic guest/host system. An interpenetrating polymer network (IPN) containing aligned NLO chromophores is selected to test these issues. An IPN is a structure in which two or more networks are physically combined.¹²⁻¹⁴ The IPN is known to be able to remarkably suppress the creep and flow phenomena in polymers. The motion of each type of polymer in the IPN is reduced by the entanglements between the networks.

The IPN system consists of an NLO active epoxy-based polymer network and an NLO active phenoxy-silicon polymer network.^{15,16} The

epoxy-based NLO network is prepared from the epoxy prepolymer (BPAZO) based on the diglycidyl ether of bisphenol A and 4-(4'-nitrophenylazo)aniline functionalized with crosslinkable acryloyl groups.⁷ The second NLO network of a phenoxy-silicon polymer is based on an alkoxy silane dye (ASD)¹⁷ of (3-glycidoxypropyl)trimethoxysilane and 4-(4'-nitrophenylazo)aniline, and the multifunctional phenoxy molecule 1,1,1 - tris (4-hydroxyphenyl)ethane (THPE).⁹ The chemical structures of BPAZO, ASD, and THPE are shown in Figure 1. The IPN is formed simultaneously upon heating where the epoxy-based polymer network is formed through double reaction and the phenoxy-silicon polymer network is formed through sol-gel reaction.

(Insert Figure 1)

The T_g of the IPN was determined to be 176 °C by differential scanning calorimetry. The corona poling technique^{3,4,7} was employed to align the NLO chromophores. Poling and curing were performed simultaneously at 200 °C for 1 h. The second-order NLO properties of the poled IPN samples were measured by second harmonic generation from 1.064 μm laser radiation. The relaxation behavior of the second-order NLO properties was studied by monitoring the decay of the SH intensity as a function of time at different temperatures (from 110 °C to 170 °C) 24 h after poling and curing to avoid any space charge effect. The NLO coefficient, d_{33} , of the poled IPN sample was measured to be 33 pm/V and 5.5 pm/V at an incident fundamental wavelength of 1.064 and 1.542 μm respectively.

Figure 2 shows the decay of the d_{33} coefficient as a function of time at different temperatures for the IPN samples. The time $t=0$ was defined as the time when the samples were brought to the desired temperatures for the relaxation study. The IPN system shows no measurable decay of SH intensity after being heated at 110 °C for 168 h. An attempt was made to fit the experimental data at higher temperatures to the KWW equation which is often used to characterize the orientational relaxation in polymers.¹⁸ The KWW equation can be written as¹¹

$$d_{33}(t)/d_{33}(0) = e^{-(t/\tau)^\beta} \quad 0 < \beta \leq 1$$

where β determines the width of the distribution of relaxation times about some central value. The characteristic relaxation time τ is the time required for the system to decay to $1/e$ of its initial value. The equation fits the decay curves very well only for temperatures in the vicinity of T_g (range from 140 to 170 °C) shown as solid lines in Figure 2 with β values falling in a range of 0.3 to 0.4 and the τ values in a range of 10^4 to 10^6 sec. The data from experiments at 120 and 130 °C do not fit the KWW equation and attempted fits result in large deviations from the data. The extremely slow decay of d_{33} at temperatures lower than 130 °C corresponds to very long relaxation times.

(Insert Figure 2)

Figure 3 shows a plot of $\log \tau$ as a function of $1/(T_g - T)$ using the equation shown below:

$$\tau = \tau_0 e^{[B/(T_g - T)]}$$

The dashed line represents the data for the guest/host type samples reported by Stähelin et al.¹¹ An arrow indicates the temperature at 110 °C, at which no decay of the SH coefficient was observed after a period of 168 h. The error bar for the data point at 130 °C indicates the large deviations in τ values at lower temperatures. The results show that the relaxation behavior of the IPN is significantly different from those of the guest/host type polymers. The stability of the d₃₃ coefficient for the IPN samples at low temperatures as well as temperatures close to T_g is substantially superior to the guest/host type samples. An attempt to improve the correlation between τ and T_g, especially when the temperature is close to T_g, was made by plotting log τ vs. 1/(T_g + 50 - T) as suggested by Stähelin et al.¹¹ and Walsh et al.¹⁹ The results were not significantly improved and the nature of departure was similar to that shown in Figure 3.

(Insert Figure 3)

In contrast to the guest/host systems, the relaxation times τ obtained from the KWW equation at temperatures near T_g for our IPN samples follow the Arrhenius type behavior (Figure 4). The Arrhenius equation can be written as:²⁰

$$\tau = A e^{(E_a/RT)}$$

where E_a is the activation energy for the relaxation process. The activation energy calculated from the plot for the temperature range of 140 to 170 °C in Figure 4 is 46 kcal/mole. This is a relatively small value compared to the activation energy that is normally observed for the α relaxation of rigid polymers.^{21,22} It implies that the dipolar relaxation in this temperature range follows Arrhenius behavior similar to side-group

relaxations in amorphous polymers and is not associated with the main chain motion. As the temperature decreases to 110 °C, there is a significant increase in the relaxation time at some critical temperature where the relaxation phenomenon may no longer follow the Arrhenius behavior. It can be inferred from this result that there are at least two different relaxation mechanisms dominating the SH decay process for the IPN samples.

(Insert Figure 4)

We have demonstrated that the dipolar relaxation process of the IPN system is essentially different from that of a typical guest/host system. At temperatures lower than 130 °C the relaxation times significantly increase and deviate from the master line for guest/host systems. In addition, scaling the Tg to Tg + 50 °C does not reduce the data points to the master curve (Figure 3). The decay of nonlinearity of the IPN system at temperatures close to Tg is inherently a slower process than the guest/host system. This property allows for high temperature spikes, which maybe encountered during device fabrication. The extensive crosslinking and chain entanglements in the IPN are responsible for the enhancement of the stability. The combination of high Tg polymers and the IPN architecture is believed to further improve the temporal stability. This area of research is currently being investigated in our laboratory.

ACKNOWLEDGMENT

Partial funding from ONR is gratefully acknowledged.

REFERENCES

1. Eaton, D. F. *Science* **1991**, 253, 281.
2. Twieg, R. J.; Jain, K. In *Nonlinear Optical Properties of Organic and Polymeric Materials*; Williams, D. J., Ed., ACS Symposium Series 233; American Chemical Society: Washington, DC, 1982; p 57.
3. Singer, K. D.; Sohn, J. E.; Lalama, S. J. *Appl. Phys. Lett.* **1986**, 49, 248.
4. Eich, M.; Reck, B.; Yoon, D. Y.; Willson, C. G.; Bjorklund, G. C. *J. Appl. Phys.* **1989**, 66, 3241.
5. Wu, J. W.; Valley, J. F.; Ermer, S.; Binkley, E. S.; Kenney, J. T.; Lipscomb, G. F.; Lytel, R. *Appl. Phys. Lett.* **1991**, 58, 225.
6. Mandal, B. K.; Kumar, J.; Huang, J. C.; Tripathy, S. K. *Makromol. Chem., Rapid Commun.* **1991**, 12, 63.
7. Jeng, R. J.; Chen, Y. M.; Kumar, J.; Tripathy, S. K. *J. Macromol. Sci., Pure Appl. Chem.* **1992**, A29, 1115.
8. Hayden, L. M.; Sauter, G. F.; Ore, F. R.; Pasillas, P. L.; Hoover, J. M.; Lindsay, G. A.; Henry, R. A. *J. Appl. Phys.* **1990**, 68, 456.
9. Jeng, R. J.; Chen, Y. M.; Chen, J. I.; Kumar, J.; Tripathy, S. K. *Macromolecules* **1993**, 26, 2530.
10. Hampsch, H. L.; Yang, J.; Wong, G. K.; Torkelson, J. M. *Macromolecules* **1990**, 23, 3640.
11. Stähelin, M.; Burland, D. M.; Ebert, M.; Miller, R. D.; Smith, B. A.; Twieg, R. J.; Volksen, W.; Walsh, C. A. *Appl. Phys. Lett.* **1992**, 61, 1626.
12. Sperling, L. H. *Interpenetrating Polymer Network and Related Materials*; Plenum Press: New York, 1981.
13. Manson, J. A.; Sperling, L. H. *Polymer Blends and Composites*; Plenum Press: New York, 1976; Chapter 8.

14. Klempner, D.; Berkowski, L. In *Encyclopedia of Polymer Science and Engineering*, 2nd ed.; Mark, H. F., Bikales, N. M., Overberger, C. G., Menges, G., Kroschwitz, J. I., Eds.; Wiley, New York, 1986; Vol. 8, pp 279-341.
15. Marturunkakul, S.; Chen, J. I.; Li, L.; Jeng, R. J.; Kumar, J.; Tripathy, S. K. *Chem. Mater.* **1993**, *5*, 592.
16. Marturunkakul, S.; Kumar, J.; Tripathy, S. K. *Proc. Am. Chem. Soc., Div. Polym. Mat.: Sci. & Eng.* **1993**, *69*, 436.
17. Jeng, R. J.; Chen, Y. M.; Jain, A. K.; Kumar, J.; Tripathy, S. K. *Chem. Mater.* **1992**, *4*, 1141.
18. Chung, S.; Stevens, J. R. *Am. J. Phys.* **1991**, *59*, 1024.
19. Walsh, C. A.; Burland, D. M.; Lee, V. Y.; Miller, R. D.; Smith, B. A.; Twieg, R. J.; Volksen, W. *Macromolecules* **1993**, *26*, 3720.
20. Nozaki, R.; Mashimo, S. *J. Chem. Phys.* **1987**, *87*, 2271.
21. Blythe, A. R. in *Electrical properties of polymers*; Cambridge University Press: Cambridge, 1979; p 52.
22. Chen, C. K.; Liepins, R. *Electrical Properties of Polymers*; Hanser Publishers: New York, 1987; p 95.

List of Figures

FIG. 1 The chemical structures of BPAZO, ASD, and THPE.

FIG. 2 Temporal behavior of the second harmonic coefficient of the IPN at different temperatures.

FIG. 3 Relaxation time τ as a function of $1/(T_g-T)$ for the IPN samples at 130, 140, 150, 160, and 170 °C. The dash line is the master curve from ref. 11 that is expected to fit guest/host system.

FIG. 4 An Arrhenius plot for the relaxation of the IPN at 130, 140, 150, 160, and 170 °C. An arrow showing 110 °C indicates the temperature at which no measurable decay of the d_{33} could be observed.

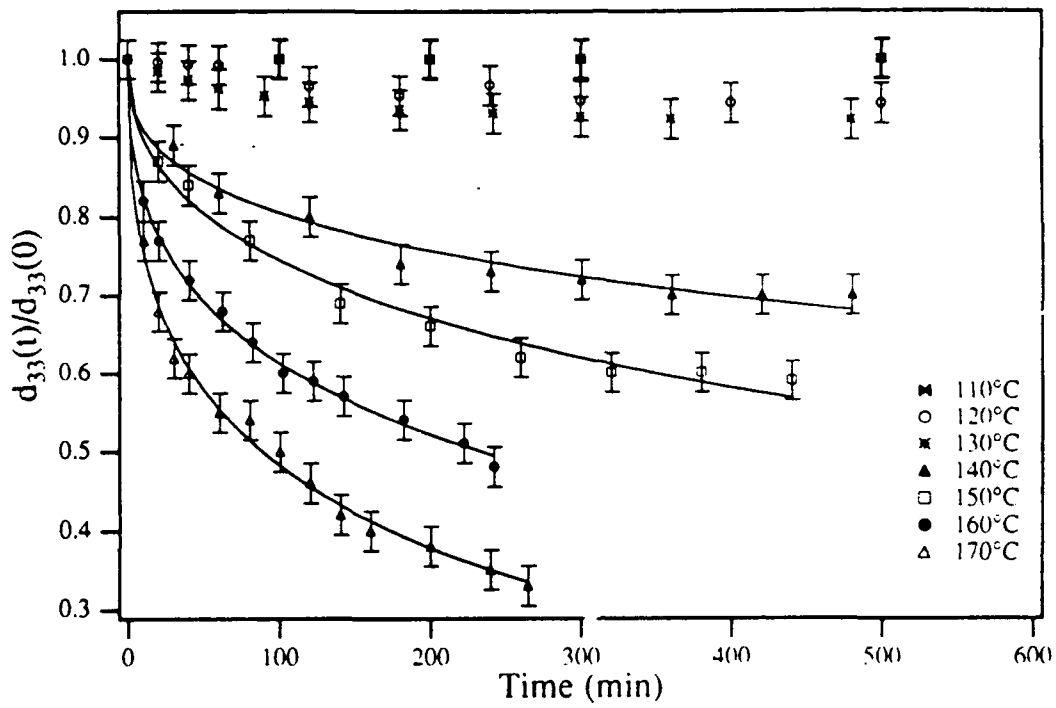


Fig 2

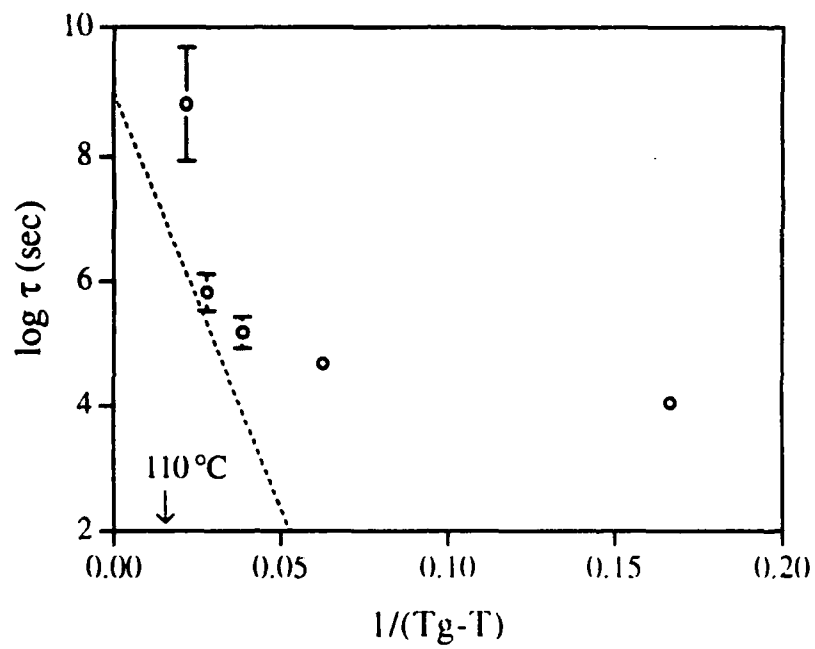


Fig. 3

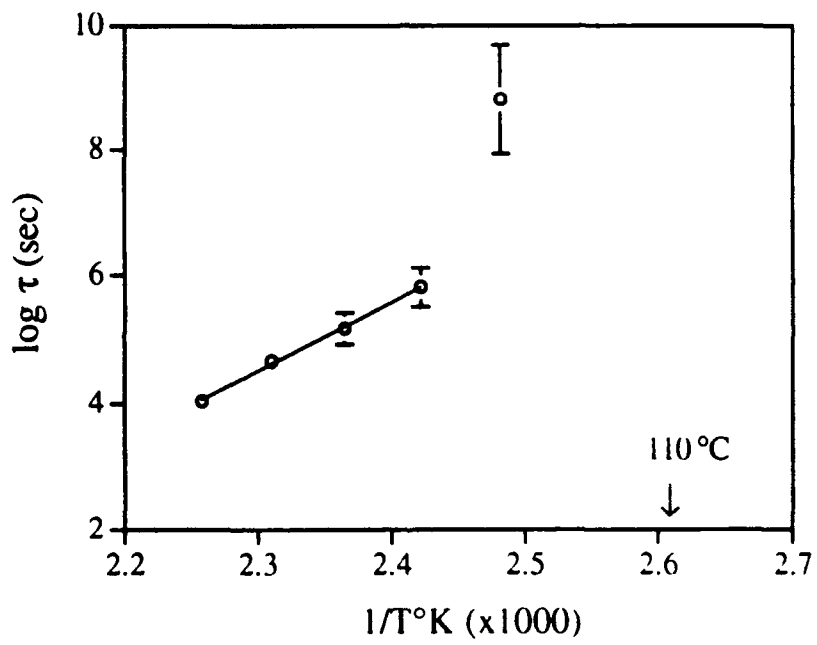


Fig. 4

Office of Naval Research (1)
Chemistry Division, Code 313
800 North Quincy Street
Arlington, VA 22217-5000

Dr. James S. Murday (1)
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, DC 20375-5000

Dr. Robert Green, Dir. (1)
Chemistry Division, Code 385
Naval Weapons Center
Weapons Division
China Lake, CA 93555-6001

Defense Technical Information Center (2)
Building 5, Cameron Station
Alexandria, VA 22314

Dr. Bernard E. Douda (1)
Crane Division
Naval Surface Warfare Center
Crane, IN 47522-5000

Dr. Richard W. Drisko (1)
Naval Civil Engineering Laboratory
Code L52
Port Hueneme, CA 93043

Dr. Harold H. Singerman (1)
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Dr. Eugene C. Fischer (1)
Code 2840
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Dr. Elek Lindner (1)
Naval Command,
Control and Ocean Surveillance Center
RDT&E Division
San Diego, CA 92152-5000