

①



Use 1 hour per volume, including the time for reviewing instructions, searching existing data sources, gathering of information, and comments regarding the burden estimates or any other aspect of this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Avenue, Washington, DC 20540, and Budget Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE July 13, 1994		3. REPORT TYPE AND DATES COVERED Technical Report #3	
4. TITLE AND SUBTITLE Enhancement of Luminescence in Polymer Nanocomposites				5. FUNDING NUMBERS N00014-94-1-0540	
6. AUTHOR(S) S.A. Jenekhe and J.A. Osaheni				R & T Code: 3132111	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Department of Chemical Engineering University of Rochester 206 Gavett Hall Rochester, NY 14627-0166				8. PERFORMING ORGANIZATION REPORT NUMBER #3	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Office of Naval Research 800 North Quincy Street Arlington, VA 22217-5000				10. SPONSORING/MONITORING AGENCY REPORT NUMBER 94-23456	
11. SUPPLEMENTARY NOTES Prepared for Publication in <u>Chemistry of Materials</u> .					
12a. DISTRIBUTION/AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The effect of supramolecular structure and morphology on the solid state luminescence of polymers is explored through a rod-coil copolymer system, poly(benzobisthiazole-1,4-phenylene-co-benzobisthiazole decamethylene), which forms nanocomposites at compositions below 50 mol% rods. The composition dependence of the photoluminescence quantum efficiency exhibited a sharp change corresponding to a change in supramolecular structure of the copolymers. The photoluminescence quantum efficiency of the polymer nanocomposites was as high as 37% which represents over sixfold enhancement compared to the corresponding "bulk" conjugated polymer. These results have implications for the fundamental understanding of the origin of luminescence quenching in conjugated polymers and they also suggest that control of supramolecular structure and morphology is key to efficient solid state luminescence in polymers.					
14. SUBJECT TERMS Polymer nanocomposites; rod-coil copolymers; luminescence; supramolecular structure; morphology; quantum efficiency; conjugated polymers				15. NUMBER OF PAGES 15	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified		18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified		19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	
				20. LIMITATION OF ABSTRACT Unlimited	

DTIC
 ELECTE
 JUL 27 1994
 S G D

1888



OFFICE OF NAVAL RESEARCH

GRANT N00014-94-1-0540

R&T Code 3132111

Kenneth J. Wynne

Technical Report No. 3

Enhancement of Luminescence in Polymer Nanocomposites

by

Samson A. Jenekhe and John A. Osaheni

Prepared for Publication

in

Chemistry of Materials

University of Rochester
Department of Chemical Engineering
Rochester, NY

July 13, 1994

Accession For	
NTIS CRA&J	<input checked="" type="checkbox"/>
DTIC TAB	<input checked="" type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution /	
Availability Codes	
Dist	Avail and/or Special
A-1	

Reproduction in whole or in part is permitted for any purpose of the United States Government

This document has been approved for public release and sale; its distribution is unlimited.

ENHANCEMENT OF LUMINESCENCE IN POLYMER NANOCOMPOSITES

Samson A. Jenekhe* and John A. Osaheni
Department of Chemical Engineering and Center
for Photoinduced Charge Transfer
University of Rochester
Rochester, New York 14627-0166 USA

Abstract

The effect of supramolecular structure and morphology on the solid state luminescence of polymers is explored through a rod-coil copolymer system, poly(benzobisthiazole-1,4-phenylene-co-benzobisthiazole decamethylene), which forms nanocomposites at compositions below 50 mol% rods. The composition dependence of the photoluminescence quantum efficiency exhibited a sharp change corresponding to a change in supramolecular structure of the copolymers. The photoluminescence quantum efficiency of the polymer nanocomposites was as high as 37% which represents over sixfold enhancement compared to the corresponding "bulk" conjugated polymer. These results have implications for the fundamental understanding of the origin of luminescence quenching in conjugated polymers and they also suggest that control of supramolecular structure and morphology is key to efficient solid state luminescence in polymers.

*To whom correspondence should be addressed.

The light-emitting properties of polymers are currently of wide interest¹⁻¹⁰ following the report¹ that conjugated polymers can be used to fabricate light-emitting diodes (LEDs). Interest in luminescent organic dye molecules is also high as an alternative approach to molecular LEDs¹¹⁻¹⁶. Although fluorescent organic dyes exhibit very high luminescence quantum efficiencies compared to π -conjugated polymers¹⁶, the later materials are more desirable because of their robust mechanical properties, thermooxidative stability, and ease of fabrication into large area or flexible devices¹⁻⁴. There is thus a growing need for more efficient luminescent polymeric materials and a fundamental understanding of the structural factors that govern efficient light emission in polymers. Here, we report on the luminescence of novel polymer nanocomposites consisting of random rod-coil copolymers, poly(benzobisthiazole-1,4-phenylene)-*co*-poly(benzobisthiazole decamethylene), in which 2-10 nm long electroactive and photoactive rodlike segments of benzobisthiazole-1,4-phenylene chromophores are dispersed in the matrix of the flexible coil segments. The photoluminescence quantum efficiency of the polymer nanocomposites was as high as 37% which represents over sixfold increase compared to the corresponding "bulk" conjugated polymer. These results suggest that control of supramolecular structure and morphology is the key to efficient luminescence and photophysical properties of polymers.

The photophysics¹⁻¹⁶, especially luminescence, of organic dye molecules and π -conjugated polymers is currently being investigated in connection with their application as emitters in electroluminescent devices. Many dye molecules in the form of evaporated thin films¹¹⁻¹⁴ or as solid solutions in polymers (i.e. "molecularly doped" polymers)¹⁵ exhibit high photoluminescence (PL) quantum efficiency (Φ_f), good charge transport of injected or photogenerated carriers, but poor mechanical strength and thermal oxidative stability¹¹⁻¹⁶. Conjugated polymers, on the other hand, have excellent mechanical properties, thermal stability, and good processing characteristics¹⁻¹⁰. However, the *solid state* Φ_f values of current π -conjugated polymers are rather low, of order 10⁻³% to 10%, which is

from one to several orders of magnitude smaller than those of highly fluorescent dyes^{6,7,16}. We have previously reported that several π -conjugated rigid-rod polymers exhibit PL quantum efficiency of 100% in solution but only 5-10% in solid films⁷. Others have similarly found that soluble derivatives of poly(p-phenylene vinylene) have Φ_f values of order 50-60% in solution but much lower values (5-10%) in thin films⁶. There is clearly a need to bridge this gap between the *solid state* and *solution* photoluminescence quantum efficiencies and elucidate the structural factors that govern efficient photophysical properties in polymers.

The origin of the low PL quantum yield in π -conjugated polymers has been the subject of recent studies and controversy^{5-7,9-10,16}. Among the prior explanations of photoluminescence quenching in π -conjugated polymers are: (i) intrachain defects; (ii) impurities; (iii) photochemical oxidation (in the specific case of vinylene polymers); and (iv) polaron pair formation. We recently proposed *excimer formation* as the dominant intermolecular mechanism for PL quenching in π -conjugated rigid-rod polymers¹⁷. A key prediction from the excimer mechanism is that enhancement of PL quantum yield can be achieved through control of the interchain packing distances¹⁷. Here we focus on the rod-coil copolymers and polymer nanocomposites which provide molecularly well-defined ways to explore the role of *supramolecular structure and morphology* on the luminescence of polymers.

Figure 1A shows the chemical structure of the random rod-coil block copolymer system which contains block repeat units of the conjugated rigid-rod homopolymer poly(p-phenylene benzobisthiazole) (PBZT) and the flexible-coil homopolymer poly(benzobisthiazole decamethylene) (PBTC10). The segmented rod-coil copolymers of varying composition were prepared by condensation copolymerization of varying ratios of terephthalic acid and decamethylenedicarboxylic acid with 2,5-diamino-1,4-benzenedithiol, similar to the preparation of the corresponding homopolymers¹⁸. The composition, molecular structure, and chain microstructure of the rod-coil copolymers were established by several techniques including ¹H NMR, ¹³C NMR, infrared and optical

spectroscopies as will be reported in detail in a forthcoming paper¹⁹. The morphology of the polymer nanocomposites was found to be amorphous by x-ray diffraction and polarized optical microscopy¹⁹. Figure 1B shows a model of the supramolecular structure and morphology of the polymer nanocomposites.

Films of the copolymer and homopolymers were spin casted from their solutions in nitromethane/ AlCl_3 similar to techniques described elsewhere^{18,20}. The spin coated films were washed in water and vacuum dried at 60°C. Optical absorption and steady state PL spectra were obtained with instrumentation previously described^{7,8}. The polymer films (~25-80 nm thick) on glass slides were positioned such that the emission was detected 22.5° from the incident radiation beam. The PL quantum yield Φ_f was measured by comparing the integration of the emission spectrum of a sample to a standard of known Φ_f under identical optical conditions²¹⁻²³. A thin film of 10^{-3} M 9,10-diphenylanthracene in poly(methyl methacrylate) ($\Phi_f = 83\%$)²³ was used as the fluorophore standard. Picosecond time-resolved PL decay measurements were made by using the time-correlated single photon counting technique and laser system described previously^{7,8}. All the photophysical measurements were made at room temperature.

The optical absorption spectra of films of several copolymers are shown in Figure 2A along with the spectrum of the conjugated homopolymer PBZT. The coillike nonconjugated polymer (PBTC10) does not absorb light at 340 nm or longer wavelength. What is most remarkable about the optical spectra of the copolymers at less than 50 mole % composition is their highly structured features which are due to the distribution of chromophores of different excitation energies which in turn reflect the distribution of block lengths of the rodlike π -conjugated PBZT repeat units incorporated into the copolymer chains. Much less structured absorption spectra were observed in the copolymers of 50 mole % rods or higher, but the increasing red shift of the absorption maximum was evident, reflecting the increasing block lengths of the π -conjugated chromophores as the copolymer system approaches

the PBZT homopolymer. These results also suggest that the optical absorption in the copolymers and PBZT is of molecular (excitonic) origin.

The PL emission of the rod-coil copolymers varied with composition (Figure 2B), indicating that the emission color can be tuned between the extremes of yellow (100%) and UV (<5%). The 5% copolymer emits blue whereas the 20% emits green. The nonlinear dependence of emission peak with copolymer composition reflects the similar dependence of the optical absorption on composition and both are due to the unique nanostructure and morphology of the materials. All the copolymer PL spectra in Figure 2B are broad and structureless except in the 5% composition where hints of structure are seen. This is in sharp contrast to the highly structured optical spectra of the same materials. The likely explanation of the broad and structureless emission spectra is either: excitation migration among the distribution of conjugated segments and emission from the lowest energy chromophore⁹; or some remaining aggregation of chromophores and consequent excimer type emission. However, the large variation of emission peak with copolymer composition in the 5-40% range where there is no variation of absorption maxima rules out the former explanation.

The composition dependence of the PL quantum efficiency of the copolymers is shown in Figure 3. At 50 mole % or higher when the coil-like polymer segments are dispersed in the matrix of the rod-like segments the quantum yield of the copolymers is identical to the "bulk" PBZT (~6%). The PL quantum efficiency is significantly enhanced relative to the pure PBZT at copolymer compositions in the range of 5-40%, where the nanocomposite morphology is achieved, reaching a peak of 37% for films of 20 mole % copolymer. This corresponds to over a sixfold enhancement of PL quantum efficiency. This high solid state PL quantum efficiency is already approaching values typical of chromophores in solution or even organic dye molecules. However, the solid state PL quantum yield of the polymer nanocomposites could still be increased by a factor of 2.7 to reach the 100% achieved in dilute solutions of PBZT. The observed slight decrease of the quantum yield in the 5-10%

compositions compared to the 20% copolymer is a result of phase separation and aggregation of the rodlike segments as evidenced by differential scanning calorimetry.

The observed large enhancement of the luminescence quantum yield in the polymer nanocomposites (< 50 mole %), compared to the conjugated polymer PBZT, can be explained in terms of interchromophore packing distances, excimer formation, and self-quenching which are regulated by the supramolecular structure and morphology of the materials. In the "bulk" conjugated polymer and copolymers of high composition (≥ 50 mole %), the small interchromophore distances of order 3-4 Å allow a high degree of chromophore aggregation, excimer formation, and self-quenching. At lower copolymer compositions (< 50%), where the nanocomposite morphology is attained, the rodlike π -conjugated chromophores are dispersed in the matrix of the flexible coil segments, resulting in greater interchromophore distances and consequent reduction of the degree of luminescence self-quenching.

The picosecond time-resolved PL decay dynamics of the copolymers photoexcited at 380 nm showed a remarkable composition dependence similar to the quantum yield results. The PL decay dynamics of the 20% copolymer, which had the largest quantum yield, was well described by a single exponential with a lifetime of 0.9 ns (Figure 4). The other copolymers in the nanocomposite region (5-40 mole %) deviated from the single exponential decay to varying degrees. The copolymers of higher compositions ($\geq 50\%$) had decay dynamics that were dramatically nonexponential and similar to PBZT.

Observation of large enhancement of luminescence in polymer nanocomposites has implications for fundamental understanding of efficient light emission in polymers¹⁷ and for practical application of polymers in optoelectronics. The present results support the view that the generally low photoluminescence quantum yield of π -conjugated polymers is due to intermolecular excimer formation and self-quenching facilitated by the relatively ordered aggregation of chains¹⁷. Molecular regulation of luminescence yield thus reduces to control of interchromophore packing distances and

hence the overall supramolecular structure and morphology: for example, through copolymerization, as demonstrated here or alternatively via bulky side groups. The polymer nanocomposites are new electroactive and photoactive materials whose supramolecular structure and morphology is designed to enhance solid state photophysical properties. The entire rod-coil copolymers represent new materials that unify the two prior approaches to molecular materials for devices --- dye molecules¹¹⁻¹⁶ and π -conjugated polymers¹⁻¹⁰ --- and hence should help to bridge the gap in theoretical understanding and practical applications of both classes of materials.

In summary, the effect of supramolecular structure and morphology on the solid state luminescence of polymers is explored through a rod-coil copolymer system, poly(benzobisthiazole-1,4-phenylene-co-poly(benzobisthiazole decamethylene), which forms nanocomposites at compositions below 50 mol% rods. The composition dependence of the photoluminescence quantum efficiency exhibited a sharp change corresponding to a change in supramolecular structure of the copolymers. The photoluminescence quantum efficiency of the polymer nanocomposites was as high as 37% which represents over sixfold enhancement compared to the corresponding "bulk" conjugated polymer. These results have implications for the fundamental understanding of the origin of luminescence quenching in conjugated polymers and they also suggest that control of supramolecular structure and morphology is key to efficient solid state luminescence in polymers.

This research was supported by the US Office of Naval Research and the National Science Foundation (CTS-9311741; CHE-9120001).

REFERENCES

1. Burroughes, J.H.; Bradley, D.D.C.; Brown, A.R.; Marks, R.N.; Mackay, K.; Friend, R.H.; Burn, P.L.; Holmes, A.B. *Nature* 1990, 347, 539-541.
2. Bradley, D.D.C. *Adv. Mater.* 1992, 4, 756-758.
3. Burn, P.L.; Holmes, A.B.; Kraft, A.; Bradley, D.D.C.; Brown, A.R.; Friend, R.H.; Gymer, R.W. *Nature* 1992, 356, 47-49.
4. Gusstafsson, G.; Cao, Y.; Treacy, G.M.; Klavetter, F.; Colaneri, N.; Heeger, A.J. *Nature* 1992, 357, 477-479.
5. Woo, H.S.; Graham, S.C.; Halliday, D.A.; Bradley, D.D.C.; Friend, R.H.; Burn, P.L.; Holmes, A.B. *Phys. Rev. B.* 1992, 46, 7379-7389.
6. Smilowitz, L.; Hays, A.; Heeger, A.J.; Wang, G.; Bowers, J.E. *J. Chem. Phys.* 1993, 98, 6504-6509.
7. Osaheni, J.A.; Jenekhe, S.A. *Macromolecules* 1993, 26, 4726-4728.
8. Osaheni, J.A.; Jenekhe, S.A. *Macromolecules* 1994, 27, 739-742.
9. Rauscher, U.; Bässler, H.; Bradley, D.D.C.; Hennecke, M. *Phys. Rev. B* 1990, 42, 9830-9839.
10. Hsu, J.W.P.; Yan, M.; Jedju, T.M.; Rothberg, L.J.; Hsieh, B.R. *Phys. Rev. B.* 1994 49, 712-719.
11. Tang, C.W.; VanSlyke, S.A. *Appl. Phys. Lett.* 1987 51, 913-915.
12. Tang, C.W.; VanSlyke, S.A.; Chen, C.H. *J. Appl. Phys.* 1989, 65, 3610-3616.
13. Adachi, C.; Tsutsui, T.; Saito, S. *Appl. Phys. Lett.* 1989, 55, 1489-1491.
14. Aminaka, E.; Tsutsui, T.; Saito, S.; *Jpn. J. Appl. Phys.* 1994, 33, 1061-1068; and references therein.
15. Kido, J.; Kohda, M.; Okuyama, K.; Nagai, K. *Appl. Phys. Lett.* 1992, 61, 761-763.
16. Tsutsui, T.; Saito, S. In: *Intrinsically Conducting Polymers: An Emerging Technology*, M. Aldissi, Ed., Kluwer Academic Publishers, Dordrecht, The Netherlands, 1993, pp. 123-143.

17. Jenekhe, S.A.; Osaheni, J.A. *Science*, submitted.
18. Osaheni, J.A.; Jenekhe, S.A. *Chem. Mater.* 1992, 4, 1282-1290.
19. Osaheni, J.A.; Jenekhe, S.A. manuscript in preparation.
20. Jenekhe, S.A.; Johnson, P.O.; Agrawal, A.K. *Macromolecules* 1989, 22, 3216-3222.
21. Winnik, M.A., Ed. *Photophysical and Photochemical Tools in Polymer Science*, Reidel, Dordrecht, Netherlands, 1986.
22. Demas, J.N.; Crosby, G.A. *J. Phys. Chem.* 1971, 75, 991-1024.
23. Guilbault, Ed. *Practical Fluorescence*, Marcel Dekker, New York, 1990, Chapt. 1 and 4.

FIGURE CAPTIONS


Figure 1. A - The chemical structure of rod-coil block copolymers that form polymer nanocomposites when $x/(x+y)$ is less than 0.5. B - The model of the supramolecular structure and morphology of the polymer nanocomposites, showing the assembly of rod-coil copolymer chains at one rod/coil ratio.

The morphology is controlled through the rod/coil ratio and the sizes of the rods and coils.

Figure 2. A - Optical absorption spectra of films of several copolymers (curves 1- 6) and the conjugated homopolymer (7): 1, 5%; 2, 10%; 3, 20%; 4, 30%; 5, 40%; 6, 80%; 7, 100% PBZT. B - PL spectra of PBZT and copolymers: 1, 100% PBZT; 2, 40%; 3, 20%; 4, 5%.

Figure 3. Composition dependence of PL quantum efficiency of rod-coil copolymers. Note the sharp increase of Φ_f in the nanocomposite region of composition (< 50 mole % PBZT).

Figure 4. Time-resolved PL decay dynamics of rod-coil copolymers: 1, 20%; 2, 40%; 3, 80% PBZT. The PL decay of the 20% copolymer followed a single exponential with a lifetime of 0.9 ns. The PL decay of the 80% copolymer is nonexponential as was the pure PBZT and copolymers with greater than 50% composition.

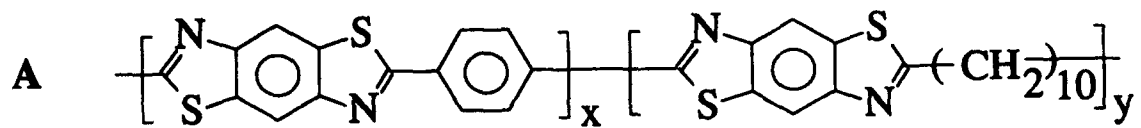

PBZT-co-PBTC10

B

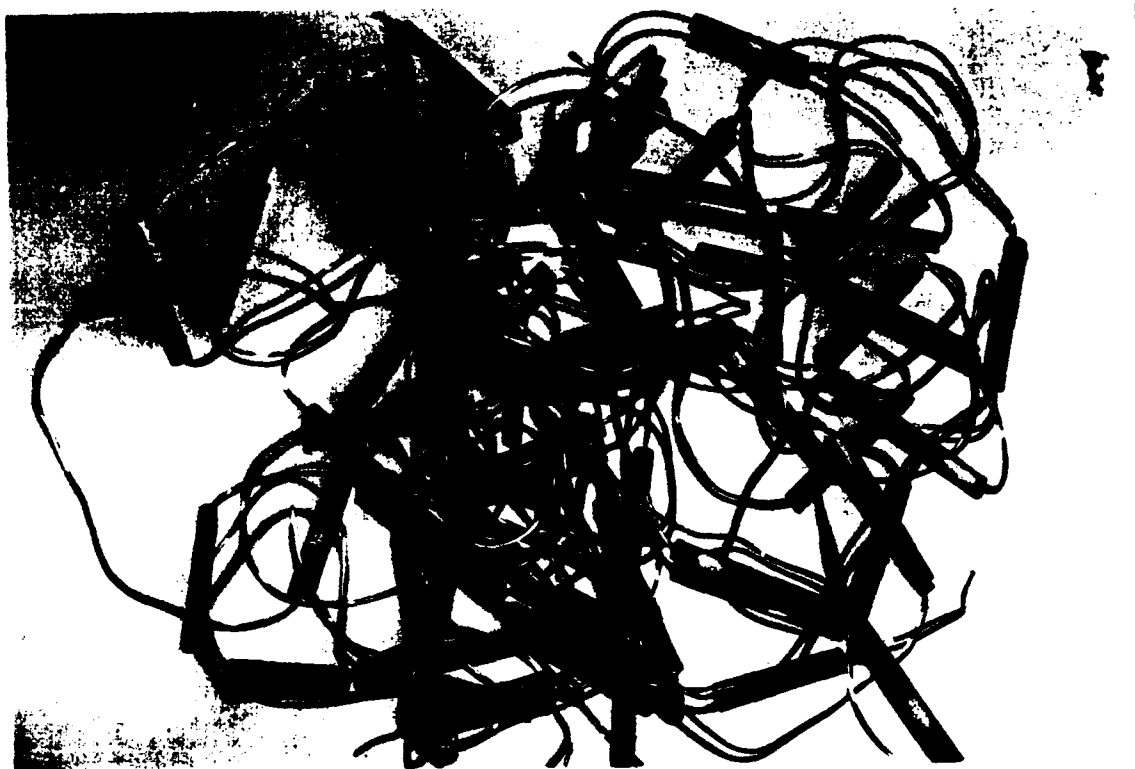


Figure 1
Jenekhe & Osaheni

Fig. 2A
Jenekhe & Osaheni

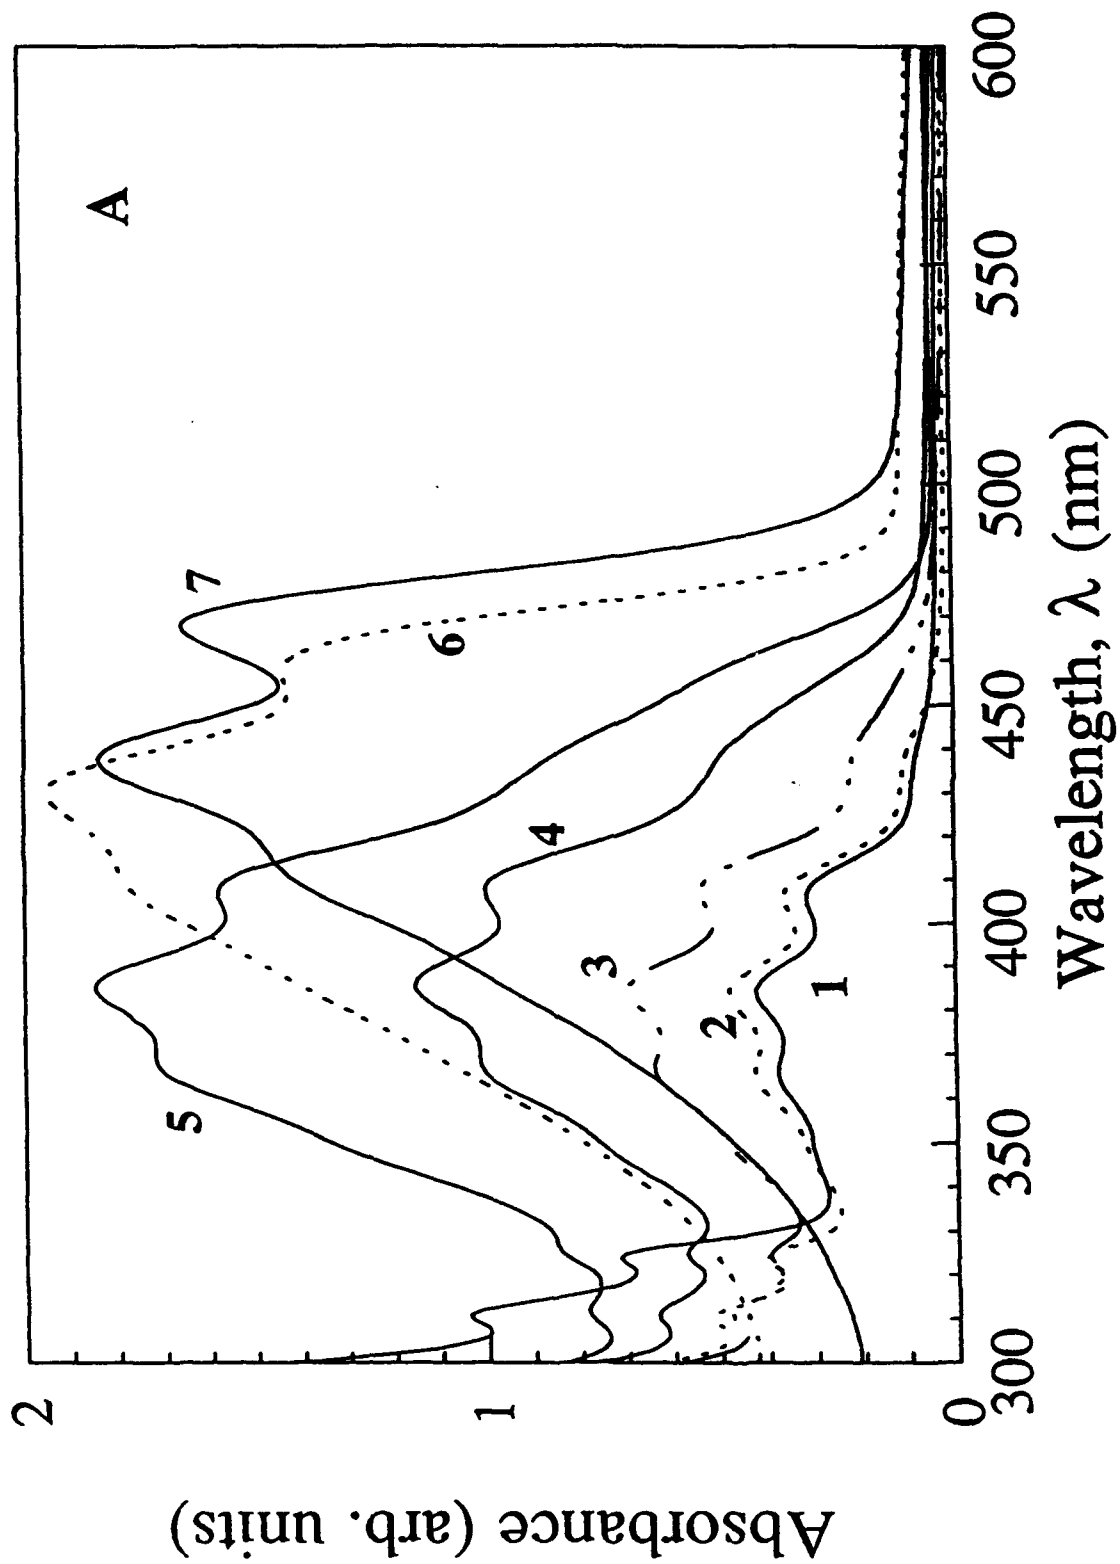


Fig. 2B
Tenekhe & Osaheni

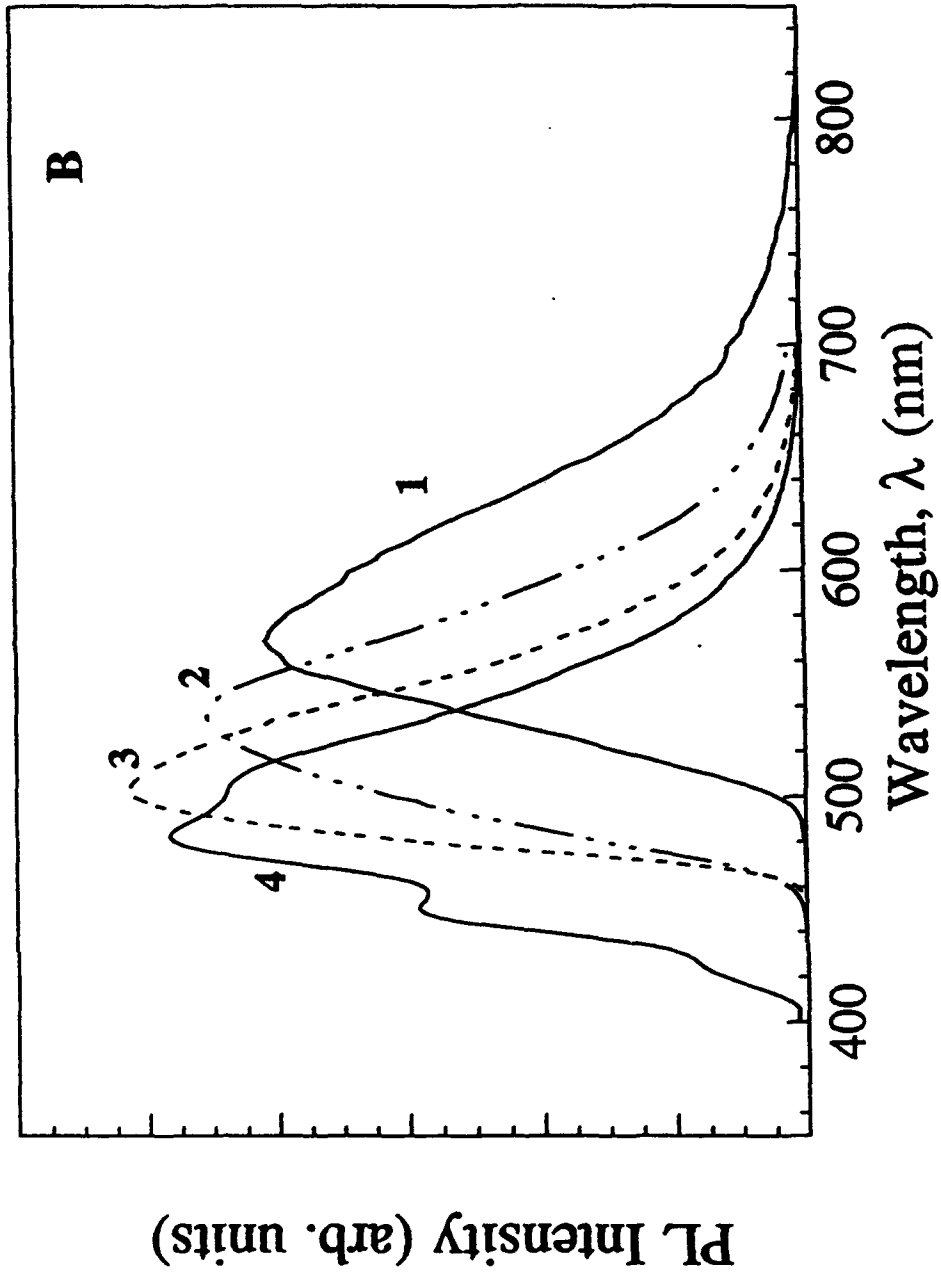


Fig. 3
Jenekhe & Osaheni


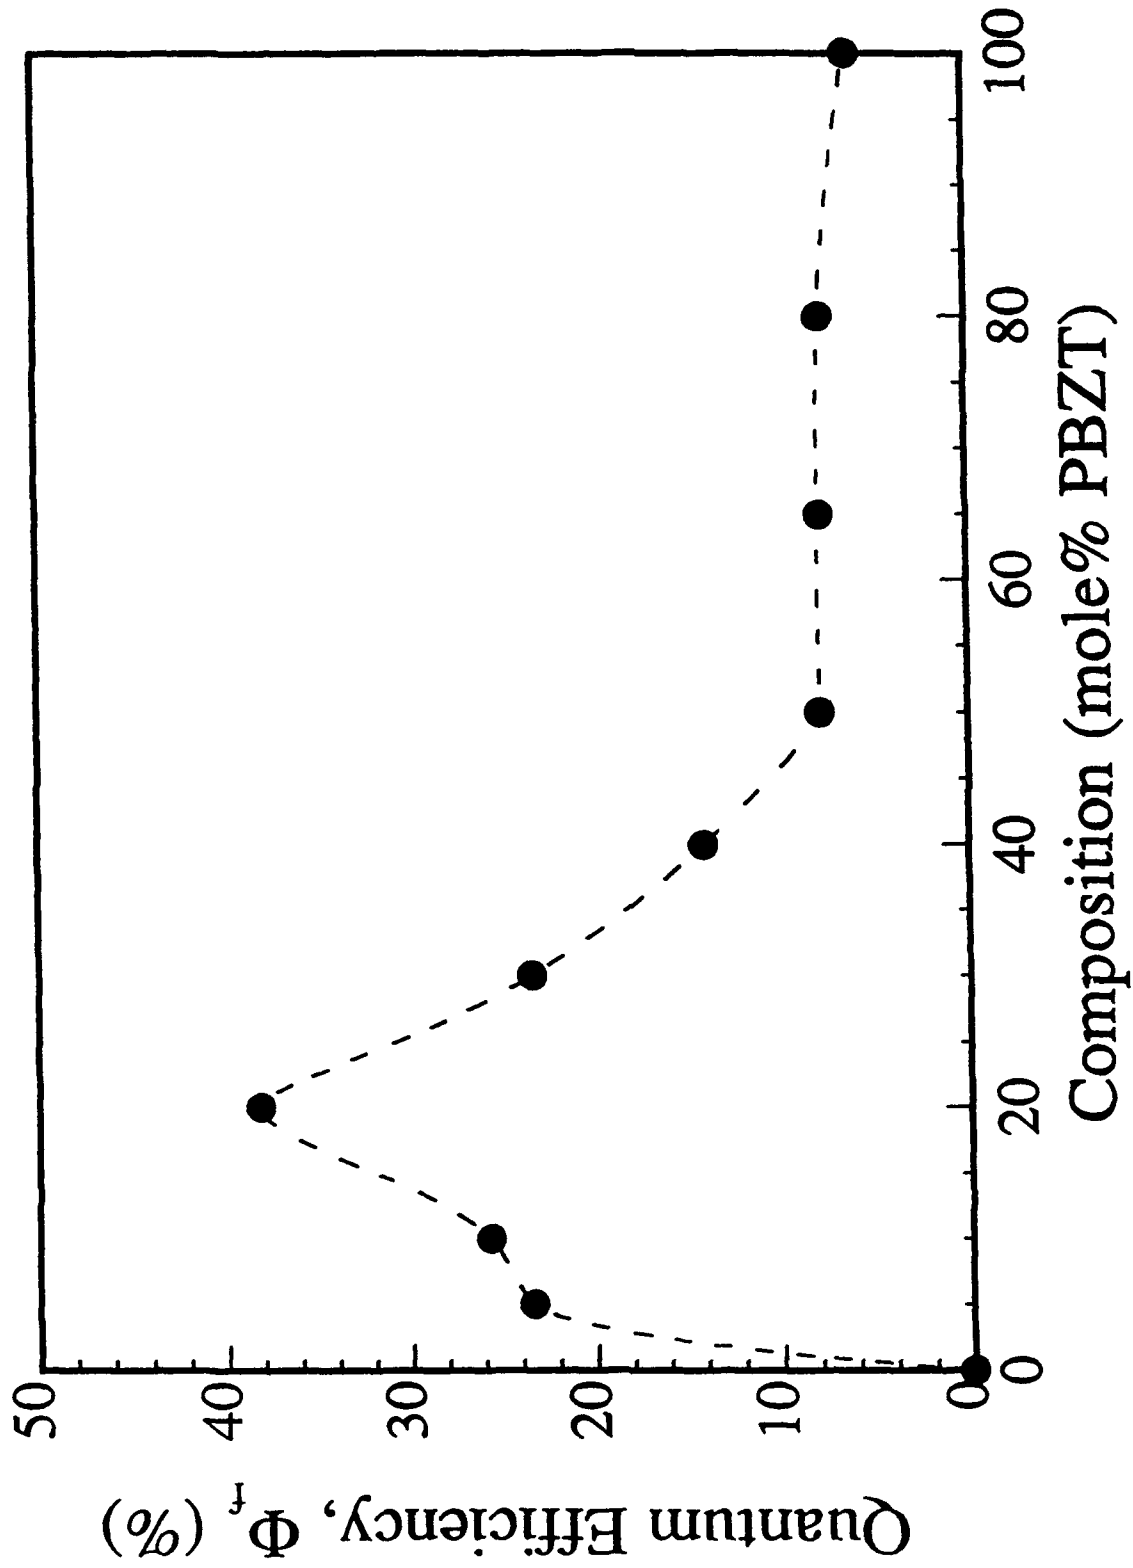


Fig. 4
Jenekhe & Osaheni

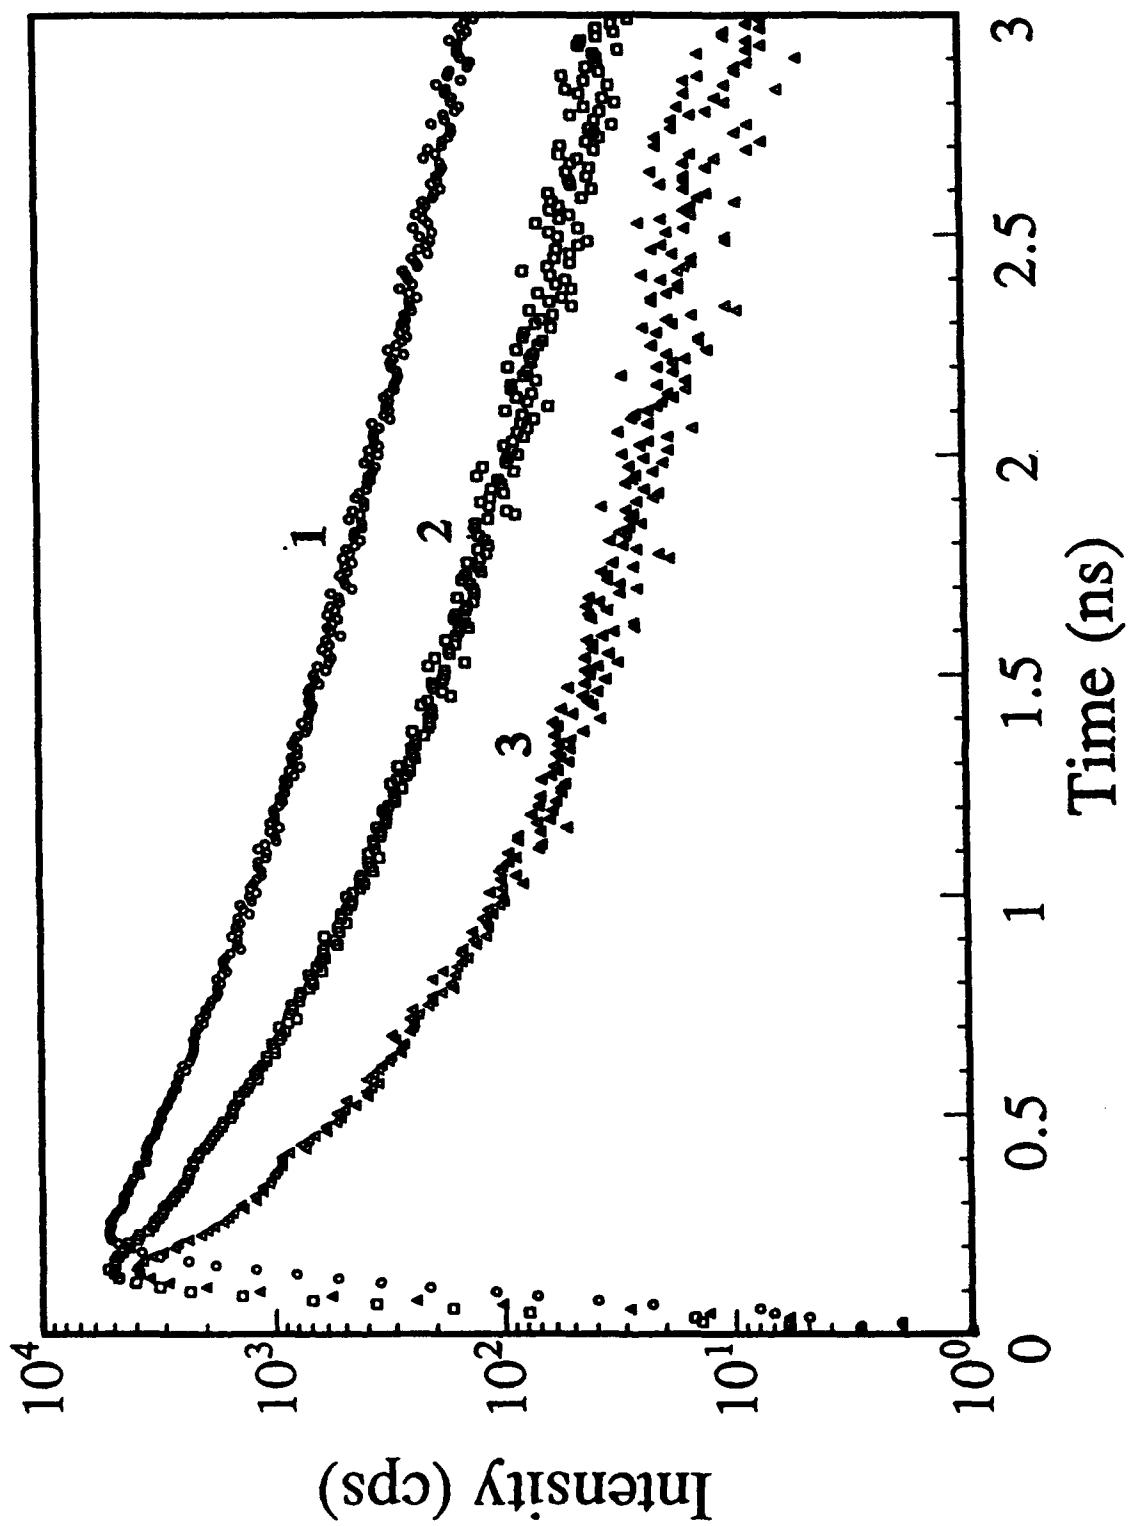

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

**Office of Naval Research (1)*
Chemistry and Physics Division
Ballston Tower 1, Room 503
800 North Quincy Street
Arlington, Virginia 22217-5660**

**Dr. Richard W. Drisko (1)
Naval Civil Engineering
Laboratory
Code L52
Port Hueneme, CA 93043**

**Defense Technical Information Center (2)
Building 5, Cameron Station
Alexandria, VA 22314**

**Dr. Harold H. Singerman (1)
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198**

**Dr. James S. Murday (1)
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, D.C. 20375-5000**

**Dr. Eugene C. Fischer (1)
Code 2840
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198**

**Dr. Kelvin Higa (1)
Chemistry Division, Code 385
Naval Air Weapons Center
Weapons Division
China Lake, CA 93555-6001**

**Dr. Peter Seligman (1)
Naval Command, Control and
Ocean Surveillance Center
RDT&E Division
San Diego, CA 92152-5000**

* Number of copies to forward