


Residual Stress in a 3D Carbon-Carbon Composite

Prepared by
L. A. FELDMAN
Materials Sciences Laboratory

30 September 1986

Prepared for
OFFICE OF NAVAL RESEARCH
800 North Quincy Street
Arlington, VA 22217
SPACE DIVISION
AIR FORCE SYSTEMS COMMAND
Los Angeles Air Force Station
P.O. Box 92960, Worldway Postal Center
Los Angeles, CA 90009-2960

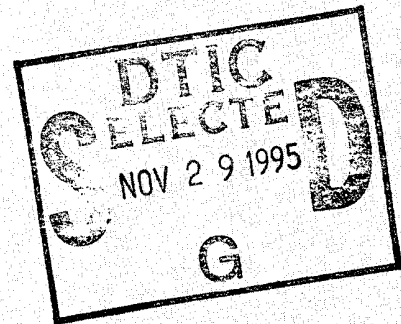

APPROVED FOR PUBLIC RELEASE;
DISTRIBUTION UNLIMITED

19951121 102

Contract No. F04701-85-C-0086

Laboratory Operations

THE AEROSPACE CORPORATION

DEPARTMENT OF DEFENSE
PLASTICS TECHNICAL EVALUATION CENTER
ARRADCOM, DOVER, N. J. 07801

DTIC QUALITY INSPECTED 5

PLASTEC 49966

LABORATORY OPERATIONS

The Aerospace Corporation functions as an "architect-engineer" for national security projects, specializing in advanced military space systems. Providing research support, the corporation's Laboratory Operations conducts experimental and theoretical investigations that focus on the application of scientific and technical advances to such systems. Vital to the success of these investigations is the technical staff's wide-ranging expertise and its ability to stay current with new developments. This expertise is enhanced by a research program aimed at dealing with the many problems associated with rapidly evolving space systems. Contributing their capabilities to the research effort are these individual laboratories:

Aerophysics Laboratory: Launch vehicle and reentry fluid mechanics, heat transfer and flight dynamics; chemical and electric propulsion, propellant chemistry, chemical dynamics, environmental chemistry, trace detection; spacecraft structural mechanics, contamination, thermal and structural control; high temperature thermomechanics, gas kinetics and radiation; cw and pulsed chemical and excimer laser development including chemical kinetics, spectroscopy, optical resonators, beam control, atmospheric propagation, laser effects and countermeasures.

Chemistry and Physics Laboratory: Atmospheric chemical reactions, atmospheric optics, light scattering, state-specific chemical reactions and radiative signatures of missile plumes, sensor out-of-field-of-view rejection, applied laser spectroscopy, laser chemistry, laser optoelectronics, solar cell physics, battery electrochemistry, space vacuum and radiation effects on materials, lubrication and surface phenomena, thermionic emission, photo-sensitive materials and detectors, atomic frequency standards, and environmental chemistry.

Computer Science Laboratory: Program verification, program translation, performance-sensitive system design, distributed architectures for spaceborne computers, fault-tolerant computer systems, artificial intelligence, micro-electronics applications, communication protocols, and computer security.

Electronics Research Laboratory: Microelectronics, solid-state device physics, compound semiconductors, radiation hardening; electro-optics, quantum electronics, solid-state lasers, optical propagation and communications; microwave semiconductor devices, microwave/millimeter wave measurements, diagnostics and radiometry, microwave/millimeter wave thermionic devices; atomic time and frequency standards; antennas, rf systems, electromagnetic propagation phenomena, space communication systems.

Materials Sciences Laboratory: Development of new materials: metals, alloys, ceramics, polymers and their composites, and new forms of carbon; non-destructive evaluation, component failure analysis and reliability; fracture mechanics and stress corrosion; analysis and evaluation of materials at cryogenic and elevated temperatures as well as in space and enemy-induced environments.

Space Sciences Laboratory: Magnetospheric, auroral and cosmic ray physics, wave-particle interactions, magnetospheric plasma waves; atmospheric and ionospheric physics, density and composition of the upper atmosphere, remote sensing using atmospheric radiation; solar physics, infrared astronomy, infrared signature analysis; effects of solar activity, magnetic storms and nuclear explosions on the earth's atmosphere, ionosphere and magnetosphere; effects of electromagnetic and particulate radiations on space systems; space instrumentation.

*MSG DI4 DROLS PROCESSING - LAST INPUT IGNORED

-- 1 OF 1

DTIC DOES NOT HAVE THIS ITEM

-- 1 - AD NUMBER: D440674
-- 5 - CORPORATE AUTHOR: AEROSPACE CORP EL SEGUNDO CA MATERIALS SCIENCES
-- LAB
-- 6 - UNCLASSIFIED TITLE: RESIDUAL STRESS IN A 3D CARBON-CARBON,
-- COMPOSITE,
--10 - PERSONAL AUTHORS: FELDMAN, L. A. ;
--11 - REPORT DATE: SEP 30, 1986
--12 - PAGINATION: 14P
--14 - REPORT NUMBER: TOR-0086(6728-02)-4
--15 - CONTRACT NUMBER: F04701-85-C-0086
--20 - REPORT CLASSIFICATION: UNCLASSIFIED
--22 - LIMITATIONS (ALPHA): APPROVED FOR PUBLIC RELEASE; DISTRIBUTION
-- UNLIMITED. AVAILABILITY: OFFICE OF NAVAL RESEARCH, 800 N. QUINCY ST.
-- , ARLINGTON, VA. 22217.
--33 - LIMITATION CODES: 1 24

-- END Y FOR NEXT ACCESSION

END

Alt-Z FOR HELP3 ANSI

3 HDX 3

3 LOG CLOSED 3 PRINT OFF 3 PARITY

| REPORT DOCUMENTATION PAGE | | READ INSTRUCTIONS BEFORE COMPLETING FORM |
|--|-----------------------|--|
| 1. REPORT NUMBER | 2. GOVT ACCESSION NO. | 3. RECIPIENT'S CATALOG NUMBER |
| 4. TITLE (and Subtitle) Residual Stress in a 3D Carbon-Carbon Composite | | 5. TYPE OF REPORT & PERIOD COVERED |
| | | 6. PERFORMING ORG. REPORT NUMBER TOR-0086(6728-02)-4 |
| 7. AUTHOR(s) L. A. Feldman | | 8. CONTRACT OR GRANT NUMBER(s) FO4701-85-C-0086 |
| 9. PERFORMING ORGANIZATION NAME AND ADDRESS The Aerospace Corporation El Segundo, CA 90245 | | 10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS |
| 11. CONTROLLING OFFICE NAME AND ADDRESS Space Division Los Angeles Air Force Station Los Angeles, CA 90009-2960 | | 12. REPORT DATE 30 September 1986 |
| | | 13. NUMBER OF PAGES 14 |
| 14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) Office of Naval Research Arlington, VA 22217 | | 15. SECURITY CLASS. (of this report) Unclassified |
| | | 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE |
| 16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited. | | |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) | | |
| 18. SUPPLEMENTARY NOTES | | |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Carbon-carbon composites Residual stress Thermal expansion mismatch 3D carbon-carbon composites | | |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Residual stress is measured in a thin slice from a carbon-carbon composite with a 3D Cartesian weave. The curvature of a slice of asymmetric cross section indicates the amount of stress caused by thermal expansion anisotropy. | | |

RESIDUAL STRESS IN A 3D
CARBON-CARBON COMPOSITE

Prepared by
L. A. Feldman
Materials Sciences Laboratory

30 September 1986

Laboratory Operations
THE AEROSPACE CORPORATION
El Segundo, CA 90245

Prepared for
OFFICE OF NAVAL RESEARCH
800 North Quincy Street
Arlington, VA 22217

SPACE DIVISION
AIR FORCE SYSTEMS COMMAND
Los Angeles Air Force Station
P.O. Box 92960, Worldway Postal Center
Los Angeles, CA 90009-2960

Contract No. FO4701-85-C-0086

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

| | |
|---------------------|-------------------------------------|
| Accession For | |
| NTIS CRA&I | <input checked="" type="checkbox"/> |
| DTIC TAB | <input type="checkbox"/> |
| Unannounced | <input type="checkbox"/> |
| Justification | |
| By | |
| Distribution / | |
| Availability Codes | |
| Dist | Avail and/or Special |
| A-1 | |

RESIDUAL STRESS IN A 3D
CARBON-CARBON COMPOSITE

Prepared




L. A. Feldman

Approved



H. A. Katzman, Head
Carbon and Polymers Department



R. W. Fillers, Director
Materials Sciences Laboratory

ACKNOWLEDGMENTS

The author would like to thank A. B. Chase and R. A. Meyer for helpful discussions. This work was supported in part by the Office of Naval Research and the Naval Surface Weapons Center.

CONTENTS

| | |
|----------------------------------|----|
| ACKNOWLEDGMENTS..... | v |
| I. INTRODUCTION..... | 1 |
| II. EXPERIMENTAL..... | 3 |
| III. RESULTS AND DISCUSSION..... | 5 |
| IV. CONCLUSION..... | 9 |
| REFERENCES..... | 11 |

FIGURES

| | | |
|----|---|---|
| 1. | X-Direction Slices of 2-2-3 Composite..... | 4 |
| 2. | Geometry of Unit Cell and Thin Slice along x-Direction from 2-2-3 Composite..... | 4 |
| 3. | Changes in Curvature versus Temperature of 0.25-mm Slice of 2-2-3 Composite..... | 7 |
| 4. | Measured Maximum Displacement versus Temperature..... | 8 |

I. INTRODUCTION

Residual stress, a well-known phenomenon in composites, is frequently caused by thermal expansion mismatch between reinforcement and matrix phases. Particularly for carbon-carbon composites, the consequences of thermal expansion can be severe. The extreme thermal expansion anisotropy of the graphite crystal perpendicular and parallel to the basal plane and the high stiffness parallel to the basal plane, can precipitate fracture in large composite structures during processing.

Given the high temperatures involved in processing, direct evidence for residual stress is difficult to obtain in such composites. Some work has been done by measuring cracking in processed cylindrical carbon-carbon composites (Ref. 1). Curvature or warping of machined bars of nonhomogeneous material is often observed when local variations of material properties create residual stress (Ref.2). This report discusses evidence for residual stress obtained by cutting thin slices from a 3D Cartesian weave carbon-carbon composite and measuring the residual curvature.

II. EXPERIMENTAL

In preparing slices of various thicknesses, we observed that some slices of less than a certain thickness would not remain straight but would warp noticeably (Fig. 1). Further investigation discovered the warping to be related to both the thickness of the slice relative to the yarn spacing and the slice's location in the bulk composite.

The material analyzed was a 2-2-3 (x-, y-, and z-directions, respectively) Cartesian weave composite, using PAN-based carbon yarn of approximately 380 GPa (55 Msi) modulus (Ref. 3). The x and y site spacings were 0.76 mm (30 mils), and the z site spacings were 0.84 mm (33 mils) (nominal values). The composite was fabricated from a 3D, carbon yarn preform by repeated densification by chemical vapor deposition and graphitization to temperatures above 2500°C. The matrix material was graphitic, and the composite had an overall methanol immersion density of $1.9 \times 10^{-3} \text{ kg/m}^3$ (1.9 g/cm^3).

Slices 27 mm long, 4 mm wide, and 0.25, 0.5, and 1 mm thick were cut from the bulk composite. The length was parallel to the x-direction, and the width was parallel to the y-direction. Some of the 0.25-mm-thick slices curved markedly (Fig. 1a); for thicker slices, the curvature was less severe. From the optical micrographs (Figs. 1 b and c) of the front and back surfaces of the slices, which display the directions of fiber reinforcement in the material, one can conclude that the curvature is caused by asymmetric fiber reinforcement of opposite faces of the thin slice coupled with residual thermal stress.

Figure 2 diagrams the geometry of a unit cell. The site spacing along the thickness direction of the slice corresponds to 0.76 mm (30 mils). Thus, a slice cut thinner than that will contain only part of a unit cell through the thickness. Because the location of the slice was selected at random, the amount of x-direction reinforcing carbon fiber versus matrix material and y- and z-direction reinforcing fiber was somewhat variable in the slice.

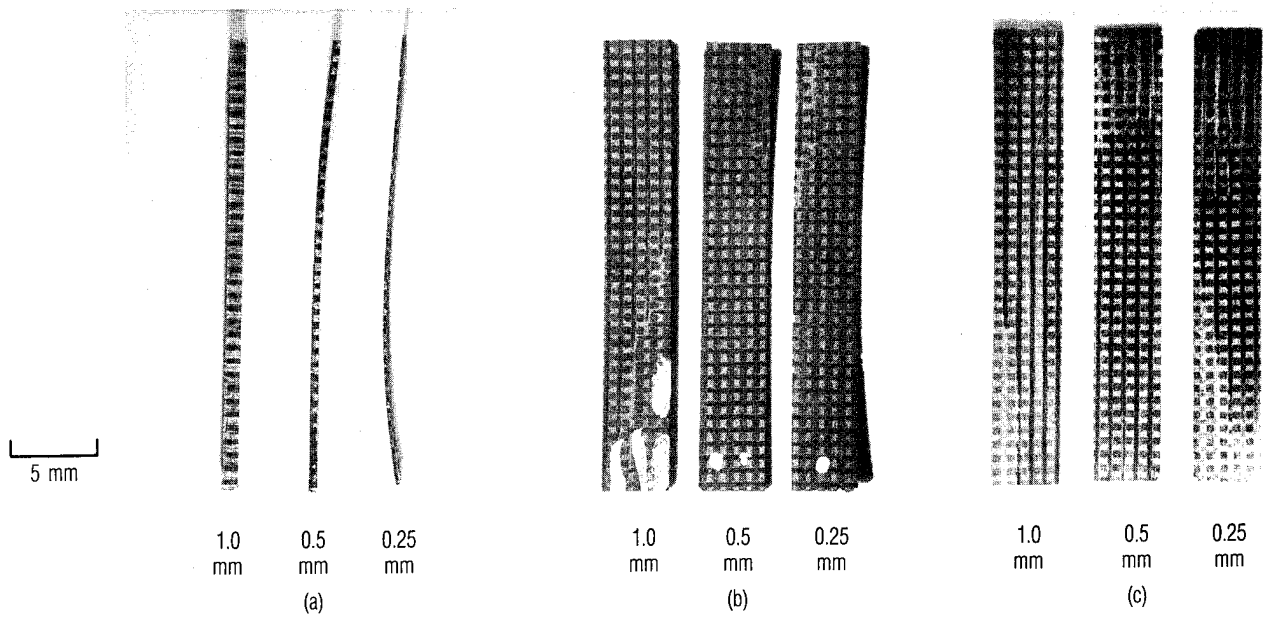


Figure 1. X-Direction Slices of 2-2-3 Composite

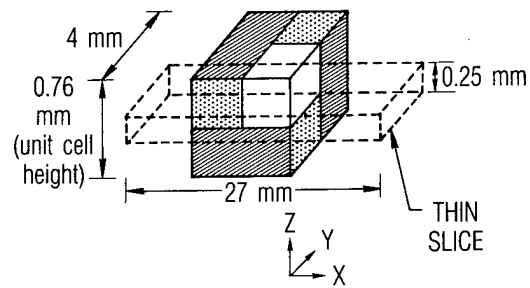


Figure 2. Geometry of Unit Cell and Thin Slice along x-Direction from 2-2-3 Composite

III. RESULTS AND DISCUSSION

In Figs. 1 b and c, x-direction reinforcing filaments in the 0.25-mm-thick slice are evident along almost the entire back surface, but none is showing on the front, although y-direction reinforcing fibers are. Matrix pockets and ends of z-direction filaments appear on both front and back faces. Because of the thermal expansion anisotropy of the fiber, the matrix and transverse directions of the y- and z-yarns in this sample tend to shrink more in cooling from elevated temperature than the longitudinal direction of the x-yarns; so the x-direction yarns are in residual compression while the matrix and transverse fibers are in residual tension. The four components--matrix and yarns in three directions--will require good bonding under conditions of local thermal expansion mismatch to retain the residual stresses.

The x-y surface of the sample is not perfectly parallel to the x-direction yarns, so the thickness of these yarns varies along the length of the sample, as the nonuniformity of the curvature along the sample illustrates. Given both this nonuniformity, which implies variation with position of the effective bending stiffness, EI, and the asymmetry of the sample with respect to the neutral surface, the relation of the composite curvature to the individual constituent properties is not simple to analyze. However, comparison in terms of a similar beam of homogeneous, isotropic material is instructive.

Assuming a thin beam, simply supported at the ends (Ref. 4), with a beam length of 27 mm, thickness of 0.25 mm, and midpoint deflection of 0.86 mm, the maximum tensile strain ϵ_{\max} can be estimated from

$$\epsilon_{\max} = \frac{t}{2R}$$

where t is the thickness and R is the radius of curvature. Given the radius of curvature, 106 mm, which can be estimated from the deflection and length, the estimated maximum tensile strain in the material is 1.2×10^{-3} . The limited applicability of isotropic beam theory dictates the need for more

complex composite beam theory, such as the 2D laminate approach with asymmetric layup (Ref. 5); however, the estimate is reasonable by being less than the measured strain to failure of typical bulk 3D carbon-carbon composites in tensile testing (Ref. 3).

Additional evidence for residual stress is demonstrated by the bimetallic strip behavior of the sample during heating and cooling, depicted in Fig. 3 for the curved sample at different temperatures on the surface of a hot plate. On heating, the curvature decreases slightly. This is to be expected, because the thermal expansion of the fibers in the longitudinal direction is lower than that of the matrix and fibers in the transverse direction. The difference will cause the matrix and transversely oriented fibers, which are in tension, to expand more than the x-direction fibers, which are in compression. The reverse occurs on cooling the sample in liquid nitrogen (77 K), which causes a small increase in sample curvature. That the curvature returned to its initial condition at room temperature shows that the changes are reversible within the temperature range, and that, therefore, bonding integrity between the components of the composite remains good.

The change in curvature with temperature can also be related to the degree of undercooling below the stress-free temperature, at which the beam is not curved. Using a linear thermal expansion model (Ref. 6), a study of residual stress in a thin beam of copper bonded to a ceramic showed that $1/R$, where R is the radius of curvature, is proportional to the degree of undercooling below the stress-free temperature, T_s , or

$$1/R = k (T_s - T)$$

where k is a constant and T is temperature. For a small degree of curvature, the midpoint displacement, d , is proportional to $1/R$ (Ref. 7). Thus, at a given temperature, T , d is proportional to $(T_s - T)$, or

$$d = k' (T_s - T)$$

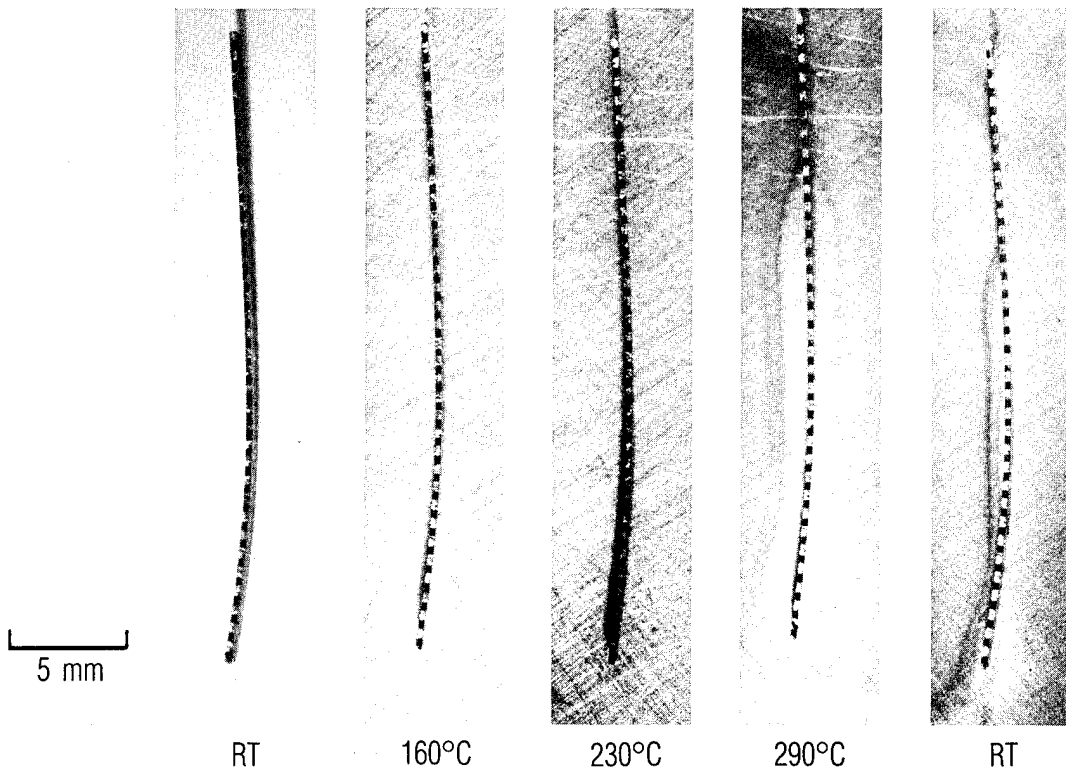


Figure 3. Changes in Curvature versus Temperature of 0.25-mm Slice of 2-2-3 Composite

where k' is a constant. From the observed values of d and T at two temperatures (e.g., room temperature and 280°C), we can solve for T_s . Thus the estimated stress-free temperature is about 1100°C (see Fig. 4), which implies that the fiber and matrix material bond well over a fairly wide temperature range and that the matrix remains sufficiently intact to retain some residual stress. The presence of residual stress and the implied large undercooling contrast with other indications that stress tends to be removed by matrix microcracking (Refs. 8 and 9) because of the large undercooling below the expected stress-free temperature, which is above 2000°C , where stress relaxation by creep becomes significant in carbon-carbon composites (Ref. 10).

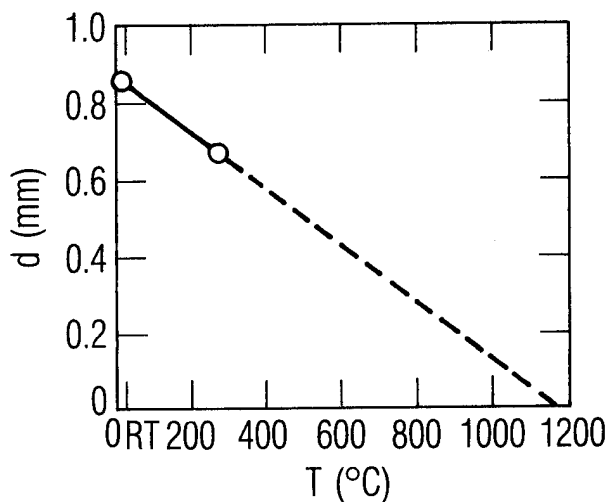


Figure 4. Measured Maximum Displacement versus Temperature

IV. CONCLUSION

In conclusion, thin slices of 3D Cartesian weave carbon-carbon composites with asymmetric cross section have been demonstrated to contain residual stresses as a result of thermal expansion anisotropy. The slices are curved, with longitudinal reinforcing filaments in residual compression and transverse fibers and matrix material in residual tension.

REFERENCES

1. G. Sines and B. J. Cohen, in Proceedings of the Symposium on Thermo-mechanical Behavior of High-Temperature Composites, ed. J. Jortner, ASME (1982), p. 63.
2. J. R. White, J. Mater. Sci. 20, 2377 (1985).
3. L. E. McAllister and W. L. Lachman, in Handbook of Composites, Ch. III of Vol. 4, "Fabrication of Composites," eds. A. Kelly and S. T. Mileiko, Elsevier, New York (1983), p. 109.
4. J. P. Den Hartog, Strength of Materials, Dover, New York (1961).
5. J. R. Vinson and T.-W. Chou, Composite Materials and Their Uses in Structures, Applied Science Publishers, Ltd., London (1975).
6. M. Wittmer, C. R. Boer, P. Gudmundson and J. Carlsson, J. Am. Ceram. Soc. 65, 149 (1982).
7. R. P. Feynman, R. B. Leighton, and M. Sands, The Feynman Lectures on Physics, Vol. 1, Addison-Wesley, Reading, Massachusetts (1963).
8. E. Fitzer and W. Huttner, J. Phys. D.: Appl. Phys. 14, 347 (1981).
9. J. Jortner, in Proceedings of the 15th Biennial Conference on Carbon, American Carbon Society (1981), p. 278.
10. L. A. Feldman, in Ext. Abstr., Proceedings of the 16th Biennial Conference on Carbon, American Carbon Society (1983), p. 499.