·						
REPORT DOCUMENTATION PAGE				UMR No 0704 0188		
Public reporting bothlan for this collar from of infor gathering and mount among the data neisled, and collecting of all similation, including suggestions to page belowing but 0.2003, order your, 9.6–22202-3	Current and the second of the second the main		conditioned to the state of	Server streams with them and 1215 influences		
1. AGENCY USE ONLY (Leave blank		3. REPORT TYPE ANI Final Technical	Report	OVERED 11/1/92-8/31/96		
a. TITLE AND SUBTITLE Organic Superconductivi and Compton Profile Spe	ity Studied by using Positr ectroscopies	on Annihilation		NG NUMBERS		
6. AUTHOR(S)	5. AUTHOR(S)					
Professor Yanching Jerry	y Jean			3484/RS		
7. PERFORMING ORGANIZATION NA	ME(S) AND ADDRESS(ES)		AF	OSR-TR-96		
University of Missouri - 5100 Rockhill Road Kansas City, MO 64110	-		\subset	568		
9. SPONSORING / MONITORING AGE	NCY NAME(S) AND ADDRESS(ES)			SORING / MONITORING		
AFOSR/ HE Building 115, Physics ar 110 Duncan Ave. Bolling AFB, DC 20332				20-92-J-0521		
122. DISTRIBUTION / AVAILABILITY S Unlimited	TATEMENT OVOG COR MERSION DE LOUIS		12b. DIS	TRIBUTION CODE		
dist: 13. ABSTRACT (Maximum 200 words	ribution noticeited.					
Organic superconductivi lifetime (PAL), and two- positron-electron moment temperature using the 2D with the Fermi surfac combination-of-atomic measured as a function of indicated from the lifeting found to be difficult to of organic superconductor	ity was studied by positron dimensional angular correl atum densities of ET-based D-ACAR method. The fold e predicted by a first-p orbitals. Positron lifetim of temperature between 1.3 me results was found at the btain a good Compton prof s. The obtained positror could be useful in providing	ation of annihilation organic supercondu ded electron densiti- rinciples method hes of ET-based on 5K and 300K. A ch e superconducting t ile at this stage due n annihilation expe	n radiati actors we es were using o ganic s nange of ransition to the la primenta	on (2D-ACAR). The ere measured at room found to be in accord orthogonalized-linear- uperconductors were felectronic density as a temperature. It was ack of large crystal of l results, along with		
14. SUBJECT TERMS				15. NUMBER OF PAGES		
	positron annihilation, Fer stronic structure	mi surfaces, momer	ntum	1.4 16. PRICE CODE		
OF REPORT	18. SECURITY CLASSIFICATION OF THIS PAGE	19. SECURITY CLASSIF OF ABSTRACT		20. LIMITATION OF ABSTRAC		
UNCLASSIFIED	UNCLASSIFIED	UNCLASSIFIE	U	andard Form 298 (Rev. 2-89)		

NSN 7540-01-280-5500

i

Standard Form 298 (Rev. 2-8 Prescribed by ANSI Std (39-18 298-102

.

Table of Contents

I.	Intro	duction	1
11	Sam	ple Preparation	1
III.	2D-A	CAR Experiments	2
IV.	Theo	pretical Calculations and the Fermi Surface	2
V.	Positron Lifetime Experiments and Calculations		
VI.	Othe	er Research Activities	2
Refe	rences		3
Figur	res		5
VII. Dat		Data Summary	
	A.	Publication	11
	В.	Presentation	11
	C.	Graduate Students	12
	Ð.	Awards	12

19961122 094

Content of Final Technical Report for AFOSR

PI: Y. C. Jerry Jean, University of Missouri - Kansas City Grant # F49620-92-J-0521 Period: 11/1/92 - 8/31/96 Total Amount: \$236,394

I. <u>Introduction</u>

The main objectives of this research project were: (1) to study the electronic properties of organic superconductors, and (2) to use the obtained electronic properties to provide some clues to search for new organic superconductors. Five research activities were performed in the project: (1) prepared organic superconductors in our laboratory at the University of Missouri - Kansas City (UMKC); (2) obtained positron-electron momentum densities in organic superconductors; (3) obtained positron lifetimes across the superconductors; (3) obtained positron lifetimes across the superconducting transition temperature (T_c) ; (4) performed a first-principles band calculation and predicted the Fermi surface; and (5) attempted experiments of the Compton profile and of K_3C_{60} .

II. Sample Preparation

Three organic superconductors (OS) were studied in this project. Their properties are listed in Table I below.

OS	T _c	Structure	a (Å)	b(Å)	c(Å)
κ-(BEDT-TTF) ₂ Cu(NCS) ₂	10.4 K	monoclinic/P2 ₁	16.25	8.440	13.12
κ-(BEDT-TTF) ₂ Cu[N(CN) ₂]Br	11.6 K	orthorhombic/Pnma	12.98	29.98	8.48
λ-(BETS) ₂ GaCl ₄	7.5 K	triclinic/P ₁	16.17	18.61	6.608

Table I. Organic Superconductors Studied in this Project

These three OS were discovered by other groups [1,2,3]. The structure of one, κ -(BEDT-TTF)₂Cu[N(CN)₂]Br, is shown in Figure 1. These OS samples were acquired from Kyoto University [1], Argonne National Labs [2], and the University of Indiana [3] for positron annihilation experiments. These crystals were well characterized by these institutions.

An electrocrystallization apparatus was installed at UMKC as described in the literature [4]. Using this set-up, the OS κ -(BEDT-TTF)₂Cu(NCS)₂ was successfully synthesized. The size of crystal was about 2 mm x 2 mm x 0.1 mm. The T_c was determined to be 7.2 K using the magnetization measurement at the University of Houston. The magnetization curve is shown in Figure 2. With this success, future development of synthesis of organic superconductors via the electrocrystallization technique has become possible at UMKC.

1

III. <u>2D-ACAR Experiments</u>

The momentum densities of an organic superconductor, κ -(BEDT-TTF)₂Cu[N(CN)₂]Br, were measured using the 2D-ACAR instruments at the University of Texas - Arlington and at UMKC [5]. Our results are the first precise measurement to search for the Fermi surface in OS using the positron technique. The results of the 2D-ACAR spectrum are reported and shown in Figure 3. The experimental data of momentum densities were the first available to quantitatively compare with the theory [6].

IV. Theoretical Calculations and the Fermi Surface

The band structure of κ -(BEDT-TTF)₂Cu[N(CN)₂]Br was calculated via a first-principles method--orthogonalizedlinear-combination-of-atomic-orbital (OLCAO)--in collaboration with Prof. W. Y. Ching at UMKC [6]. The results of the band structure and the Fermi surface are shown in Figure 4. Comparing the experiment of positron results (Fig. 3-bottom) with the theory (Fig. 4-bottom), a consistent topology was found but some fine discrepancies existed. This result is the first direct comparison between the precise 2D-ACAR experiment and a first-principles theory.

V. <u>Positron Lifetime Experiments and Calculations</u>

A He-cryostat (1.5 K - 300 K) was installed in the positron laboratory at UMKC. Positron annihilation lifetimes were measured as a function of temperature between 1.5 K and 300 K in two organic superconductors, κ -(BEDT-TTF)₂Cu(NCS)₂ and κ -(BEDT-TTF)₂Cu[N(CN)₂]Br. The positron lifetime was found to decrease as the temperature decreases below T_g [7] in both samples. This was interpreted as a local electron transfer from the insulating layer to the superconducting layer. Figure 5 shows the variations of the positron lifetime across T_c.

Extensive positron-electron density calculations were performed in these OS crystals in order to understand the positron lifetime variations. Figure 6 shows the calculated positron-electron density distributions in the κ -(BEDT-TTF)₂Cu(NCS)₂ system. A similarity of positron lifetime variation and distribution was observed between ET-based OS and oxide high temperature superconductors [8].

VI. Other Research Activities

The newly discovered OS, λ -(BETS)₂GaCl₄[3], was considered in this work. Preliminary calculations of positron and electron densities were made. The available sample size (~ 0.1 mm) was found to be too small for positron experiments. A Compton profile spectroscopy experiment was designed and prepared for the OS samples using ⁵¹Cr γ -ray sources generated at the University of Missouri Research Reactor (MURR). The initial attempt showed that the available OS crystals (mm) are too small for a good Compton profile measurement (which requires larger than 1 cm dimension) using a γ -ray source. Future development of Compton profile spectrometry using a synchrotron radiation light source may be feasible for existing OS crystals.


Other OS samples, K_3C_{60} , were also considered for positron experiments. However, sizable and good crystals of C_{60} -based superconductors were not available during the proposed period to be researched in these positron experiments <u>in-situ</u> at UMKC.

<u>References</u>

- K. Oshima, H. Urayama, H. Yamoch, and G. Saito, Physica C <u>153</u>, 1148 (1988).
- A. M. Kini, U. Geiser, H. H. Wang, K. D. Carlson, J. M. Williams, W. K. Kwok, K. G. Vandervoort, J. E. Thompson, D. L. Stupka, D. Jung, and M.-H. Whangbo, Inorg. Chem. 29, 2555 (1990).
- L. K. Montgomery, T. Burgin, J. C. Huffman, J. Ren, and M.-H. Whangbo, Physica C, <u>219</u>, 490 (1994).
- 4. J. M. Williams, J. R. Ferraro, R. J. Thorn, K. D. Carlson, U. Geiser, H. H. Wang, A. M. Kini, and M.-H. Whangbo, <u>Organic Superconductors (Including Fullerenes</u>), Prentice Hall: Englewood Cliffs, NY (1992).
- 5. Y. C. Jean, Y. Lou, H. L. Yen, K. O'Brien, R. N. West, H. H. Wang, K. D. Carlson, and J. M. Williams, Physica C, <u>221</u>, 399 (1994).
- H. L. Yen, Y. Lou, E. H. Ali, Y.-N. Xu, W. Y. Ching, H. H. Wang, K. D. Carlson, J. M. Williams, K. M. O'Brien, R. N. West, and G. Saito, Mat. Sci. Forum, <u>175-178</u>, 593 (1995).
- 7. Y. Lou, H. L. Yen, J. M. Wrobel, H. Zhang, Y. C. Jean, Z. J. Huang, C. W. Chu, and G. Saito, Phys. Rev. B, <u>49</u>, 12255 (1994).
- Y. C. Jean, C. S. Sundar, A. Bharathi, J. Kyle, H. Nakanishi, P. K. Tseng, P. H. Hor, R. L. Meng, Z. J. Huang, C. W. Chu, Z. Z. Huang, P. E. A. Turchi, R. H. Howell, A. L. Wachs, and M. J. Fluss, Phys. Rev. Lett., <u>64</u>, 1593 (1990).


Figure Captions

- Fig. 1. Crystal structure of $\kappa (ET)_2 Cu[N(CN)_2]Br$. The ET presents (BEDT-TTF) molecules.
- Fig. 2. The magnetization of κ -(BEDT-TTF)₂Cu(NCS)₂ crystals synthesized at UMKC.
- Fig. 3. The anisotropy plot of 2D-ACAR raw spectra (top) and the LCW-folded momentum density (bottom) in κ -(BEDT-TTF)₂Cu[N(CN)₂]Br crystals.
- Fig. 4. The calculated band structures (top) and predicted Fermi surfaces (bottom) of κ -(BEDT-TTF)₂Cu[N(CN)₂]Br.
- Fig. 5. The variation of positron lifetime vs temperature in κ -(BEDT-TTF)₂Cu(NCS)₂ systems.
- Fig. 6. Plots of the integrated electron density (top), positron density (middle), and positron-electron overlap (bottom) over the bc-plane vs a-axis in κ -(BEDT-TTF)₂Cu(NCS)₂ crystal, based on a first-principles OLCAO calculation.

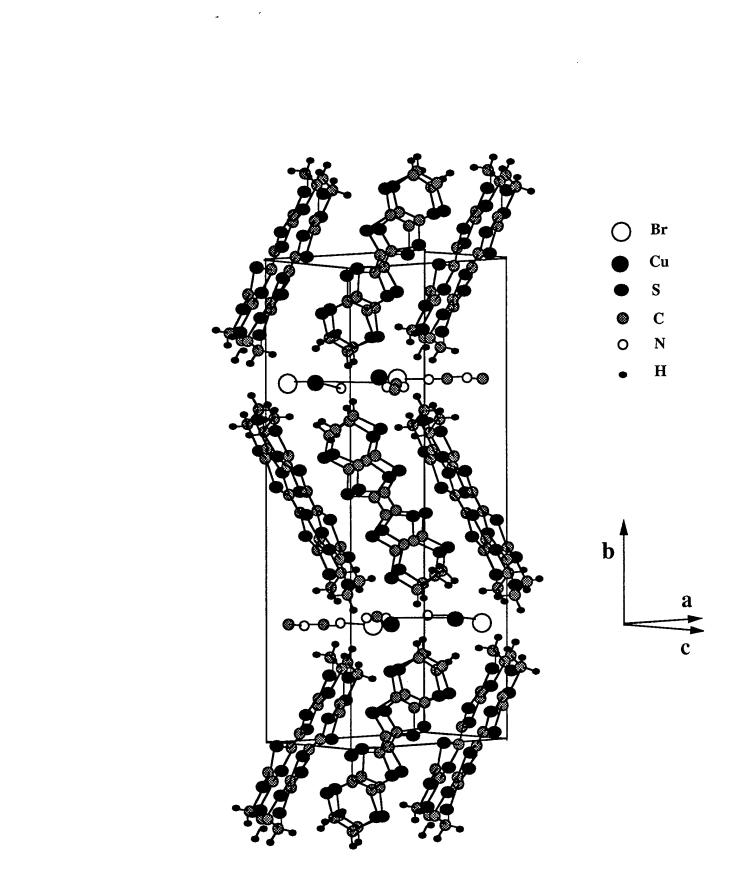


κ–ET₂ Cu[N(CN)₂]Br Structure

A change of positron lifetime at $T_{\rm c}\,\text{in}\,\,\text{k-}(\text{ET})_2\text{Cu}(\text{NCS})_2$

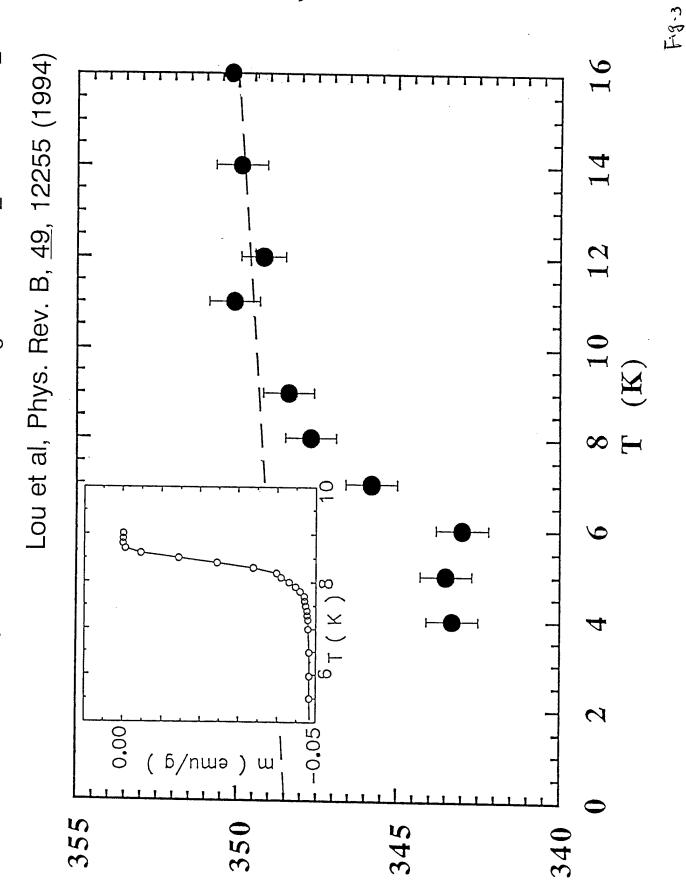


(sd) L

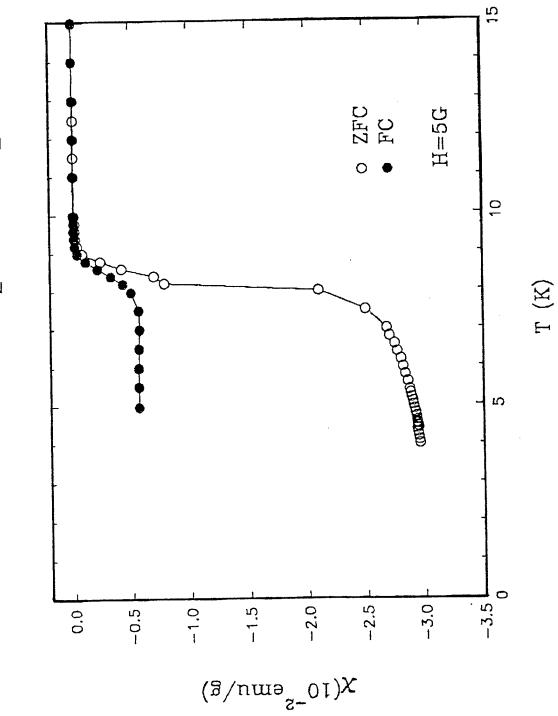


 $K-(ET)_2Cu(NCS)_2$

L


F.9.2

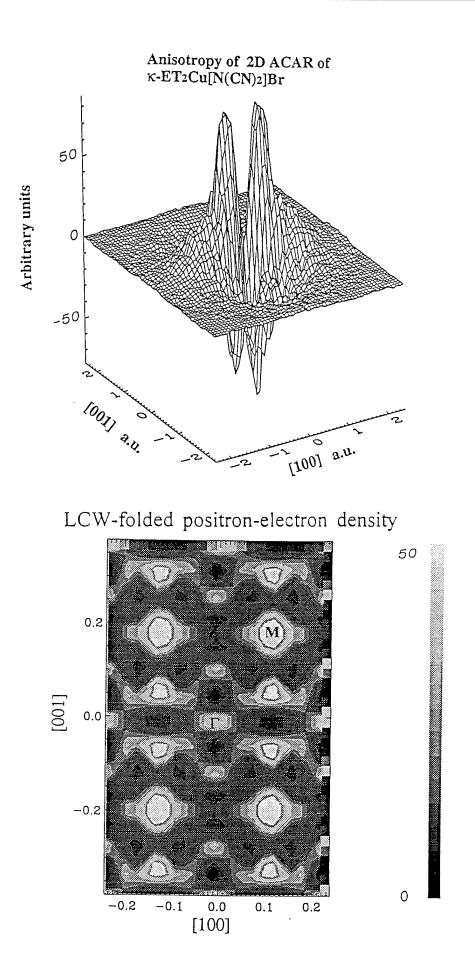


The band structures of κ -(ET)₂[N(CN)₂]Br

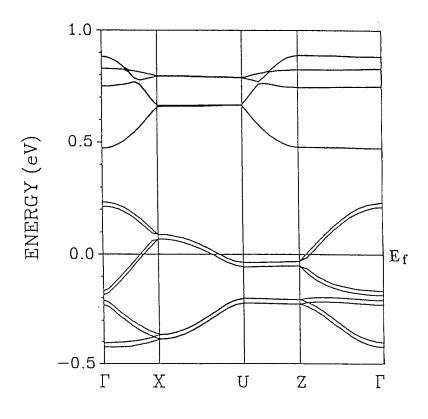

Fermi surface

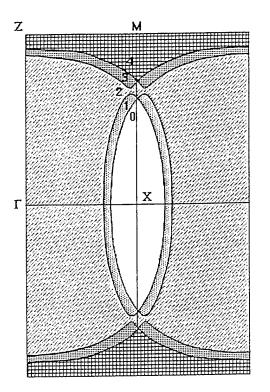

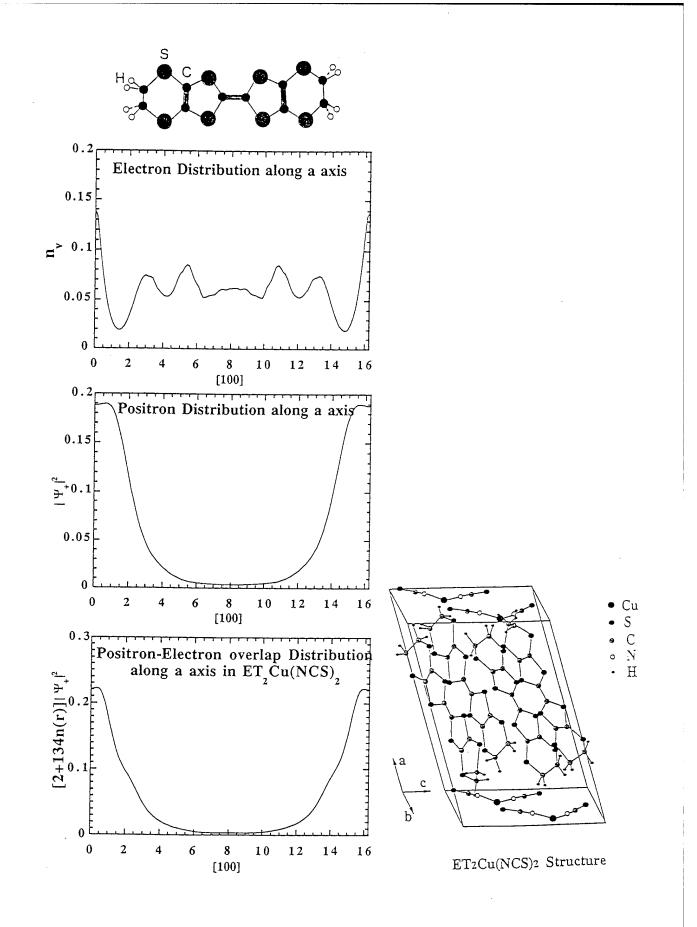

10

Fig.6

VII. Data Summary

A. Publication:

- 1. "Momentum Distribution in k-(BEDT-TTF)₂Cu[N(CN₂]Br Organic Superconductors Measured by Positron Annihilation: Search for the Fermi Surface", Physica C, <u>221</u>, 399(1994). <u>Y.C. Jean</u>, Y. Lou, H.L. Yen, K.M. O'Brien, R.N. West, H.H. Wang, K.D. Carlson, and J.M. Williams.
- "Local-Charge-Density Transfer and Organic Superconductivity: A Positron Study", Phys. Rev. B, <u>49</u>, 12255 (1994).
 Y. Lou, H.L. Yan, J.M. Wrobel, H. Zhang, and Y.C. Jean, G. Saito, Z.J. Huang, and C.W. Chu.
- 3. "Positron Annihilation Studies of Organic Superconductors", Mat. Sci. Forum <u>175-178</u>, 593 (1995). H.L. Yen, Y. Lou, E.H. Ali, T.-N. Xu, W.Y. Ching, Y.C. Jean, H.H. Wang, K.D. Carlson, J.M. Williams, K.M. O'Brien, R.N. West, and G. Saito.
- 4. "Positron Annihilation Studies of Organic Superconductors", Polymer Materials Science Engineering Division, ACS Proc. <u>72</u>, 275 (1995). H.L. Hen, Y. Lou, E.H. Ali, T.-N. Xu, W.Y. Ching, Y.C. Jean, H.H. Wang, K.D. Carlson, J.M. Williams, K.M. O'Brien, R.N. West, and G. Saito.
- Positron States in ET-Based Organic Superconductors", Y. Lou, H.L. Yen, Y.-N. Xu, W.Y. Ching, and Y.C. Jean (manuscript in preparation to be submitted to Phys. Rev. B).

B. Presentation:

- "The Fermi Surfaces in Organic Superconductors", Y. Lou, H.L. Yen, E.H. Ali, W.Y. Ching, and Y.C. Jean, March 25, APS March Meeting, Pittsburgh, PA 1994, Bull. Amer. Phys. Soc. <u>39</u>, 881 (1994).
- 2. "Electronic Structures in Organic Superconductors", H.L. Yen, Y. Lou, E.H. Ali, W.Y. Ching, and Y.C. Jean, May 28, 10th Int. Conf. Positron Annihilation, Beijing, China

- 3. "Organic Superconductivity Studied by Positron Annihilation Spectroscopy" H.L. Yen, Y. Lou, W.Y. Ching, and Y.C. Jean, Nov. 3, 1994, 29th Midwest ACS Conference, Kansas City, MO.
- 4. "Organic Superconductivity Studied by Positron Annihilation", Y. Lou, H.L. Yen, W.Y. Ching, and Y.C. Jean, Oct. 4, 1994, 42nd Midwest Solid State Conference, Kansas City.
- 5. "Organic Superconductivity studied by Positron Annihilation Spectroscopy", H.L. Yen, Y.N. Xu, W.Y. Ching, and Y.C. Jean, Bull. Amer. Phys. Soc. <u>40</u>, 774 (1995).1995, Mar. 22, American Physical Society March Meeting, San Jose, CA.
- Positron Annihilation Studies of Organic Superconductivity", H.L. Yen, Y. Lou, Y.N. Xu, W.Y. Ching, Y.C. Jean, H.H. Wang, K.D. carson, J.M. Williams, K.M. O'Brien, and R.N. West, 1995, Apr. 4, American Chemical Society Spring Meeting, Anaheim, CA.
- C. Graduate Students:
 - H.L. Yen, Ph.D. candidate in Physics/Chemistry, UMKC, "Organic Superconductors Studied by Positron Annihilation (anticipate to complete by May 1997).
 - 2. Y. Lou, M.S. Computer/Chemistry, UMKC, Dec. 1995, (non-thesis).
- D. Awards:
 - Y.C. Jean, Elected Fellow of Amer. Phys. Soc. (Dec. 1994)
 - 2. NSF grant (DMR-9402655); \$50,000; 8/15/94-7/31/96; "Fermi Surface Studies of Organic Superconductors".