

**OFFICE OF NAVAL RESEARCH**

**END-OF-THE-YEAR REPORT**

**PUBLICATIONS/PATENTS/PRESENTATIONS/HONORS/STUDENTS REPORT**

for

GRANT: N00014-97-1-0207

PR Number: 97PR03238-00

Functionalized Nanoporous Polymer Membranes with Well-Defined  
Pore Architectures via Lyotropic Liquid-Crystalline Monomers

Douglas L. Gin

University of California, Berkeley

Department of Chemistry  
Berkeley, CA 94720-1460

June 30, 1997

**DTIC QUALITY INSPECTED 5**

Reproduction in whole or in part is permitted for any use of the United States Government

This document has been approved for public release and sale; its distribution is unlimited

19970707 054

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE <b>June 30, 1997</b>	3. REPORT TYPE AND DATES COVERED <b>EOY Report June 1/96- May 31/97</b>	
4. TITLE AND SUBTITLE <b>Functionalized Nanoporous Polymer Membranes with Well-Defined Pore Architectures via Lyotropic Liquid-Crystalline Monomers</b>			5. FUNDING NUMBERS <b>Grant # N00014-97-1-0207 PR # 97PR03238-00 Dr. Kenneth J. Wynne</b>	
6. AUTHOR(S) <b>Douglas L. Gin</b>			8. PERFORMING ORGANIZATION REPORT NUMBER <b>97-01</b>	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) <b>Department of Chemistry University of California, Berkeley Berkeley, CA 94720-1460</b>				
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) <b>Office of Naval Research Physical S&amp;T Division, ONR 331 Department of the Navy Arlington, VA 22217-5000</b>			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT <b>Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.</b>			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words)  <b>Highly ordered, nanoporous polymer membranes were synthesized using polymerizable lyotropic liquid crystals that self-assemble into the inverted hexagonal mesophase as building blocks. The resulting polymer networks contain nanometer-diameter, extended hydrophilic channels that are hexagonally close-packed. Two lyotropic liquid-crystalline monomer platforms have been synthesized. The interchannel separations in the polymerizable materials can be varied in the 30-40 Å range by the choice of counterion on the ionic headgroup of the monomers. Highly oriented, monodomain thin films of these nanoporous polymers are possible via thermal processing of the liquid crystal mixtures prior to photopolymerization, which locks-in the ordered microstructure.</b>				
14. SUBJECT TERMS <b>Ordered nanoporous membranes, lyotropic liquid-crystalline monomers, photopolymerization, inverse hexagonal phase, polymerizable amphiphiles</b>			15. NUMBER OF PAGES <b>9</b>	
17. SECURITY CLASSIFICATION OF REPORT <b>Unclassified</b>			16. PRICE CODE	
			20. LIMITATION OF ABSTRACT <b>Unlimited</b>	
18. SECURITY CLASSIFICATION OF THIS PAGE <b>Unclassified</b>		19. SECURITY CLASSIFICATION OF ABSTRACT <b>Unclassified</b>		

**OFFICE OF NAVAL RESEARCH  
PUBLICATIONS/PATENTS/PRESENTATIONS/HONORS/STUDENTS REPORT**

**EOY Report – Part II**

PR Number: 97PR03238-00  
Contract/Grant Number: N00014-97-1-0207  
Contract/Grant Title: Functionalized Nanoporous Polymer Membranes with Well-Defined Pore Architectures via Lyotropic Liquid-Crystalline Monomers  
Principal Investigator: Douglas L. Gin  
Mailing Address: Dept. of Chemistry, University of California, Berkeley, CA 94720  
Phone Number: (510) 642-7756  
Fax Number: (510) 643-1846  
E-mail Address: gin@chemgate.cchem.berkeley.edu  
http address N/A

(a) Number of papers submitted to referred journals but not published: 0  
(b) Number of papers published in refereed journals 0  
(c) Number of books or chapters submitted but not yet published: 0  
(d) Number of books or chapters published: 0  
(e) Number of printed reports/non-refereed papers: 0  
(f) Number of patents filed: 0  
(g) Number of patents granted: 0  
(h) Number of invited presentations: 0  
(i) Number of submitted presentations: 0  
(j) Honors/awards/prizes for contract/grant employees: 2  
(k) Number of full time equivalent graduate students and postdoctoral associates supported during this period, under this R&T project number:

Graduate students: 0  
Postdoctoral associates 1  
Female graduate students: 0  
Female postdoctoral associates: 0  
Minority graduate students: 0  
Minority postdoctoral associates: 0  
Asian graduate students: 0  
Asian postdoctoral associates: 1

(l) Other funding (see attached list):

(j) Honor/Awards Received:

1997 Research Corporation Cottrell Scholar  
3M Untenured Faculty Award (2nd year)

(l) Other Funding Received During This Period:

U.S. Dept. of Energy, Center for Advanced Materials, Lawrence Berkeley National Laboratory; (no grant title); \$58,000 this year; total amount: \$58,000 for 1/97-10/97; unconnected to ONR grant.

Center of Excellence for the Synthesis and Processing of Advanced Materials, U.S. Dept. of Energy (no grant title); \$22,400 this year; total amount \$22,400 for 1/97-10/97

Raychem Corporation; (unrestricted research gift); \$15,000 this year; total amount: \$30,000 for 10/95-present; unconnected to ONR grant.

Junior Faculty Research Grant, Committee on Research, U. C. Berkeley; "Synthetic Composites with Tunable, Nanometer-Scale Architectures: New Materials via Monomer Self-Assembly," \$3,000 this year; total amount: \$3000 for 7/96-6/97

ACS Petroleum Research Fund; "Piezoelectric Polymer Networks via Monomer Self-Assembly;" \$10,000 for 9/1/96-8/30/97; total amount: \$20,000 for 9/1/96-8/30/98; unconnected to ONR grant.

3M Corporation; Untenured Faculty Grant (unrestricted research gift); \$15,000 this year; total amount: \$30,000 for 4/1/96-present; unconnected to ONR grant.

National Science Foundation; "Highly Ordered Polymeric Materials via Monomer Self-Assembly;" \$64,200 for 5/97-6/98; total amount: \$322,153 for 6/15/96-5/31/00; unconnected to ONR grant.

Exxon Educational Fund, unrestricted research gift, \$10,000 this year; total amount: \$10,000 for 1/97-10/97; unconnected to ONR grant.

Research Corporation, Cottrell Scholarship; "Fluorescent Chemosensors for the Detection of Biologically Active Molecules via Molecular Imprinting," \$50,000 this year; total amount: \$50,000 for 5/97-5/99; unconnected to ONR grant.

## EOY Report – Part II

- (a) Principal Investigator: Douglas L. Gin
- (b) Phone Number: (510) 642-7756
- (c) Cognizant ONR Program Officer: Dr. Kenneth J. Wynne
- (d) Program Objective:

Current polymer membrane manufacturing technologies afford extremely poor control over critical structural features such as pore size, pore architecture, and pore density in the nanometer size regime. In addition, current technologies offer few chemical alternatives to addressing the problems of membrane fouling which degrade membrane performance with use. The objective of the current research project is to develop a new class of new highly ordered, polymeric materials containing uniform pore sizes in the nanometer range using polymerizable lyotropic (i.e., amphiphilic) liquid crystals as building blocks, in which the arrangement, size, and chemical properties of the pores may be tailored on the molecular level. Specifically, our objective is to develop crosslinkable lyotropic liquid-crystalline monomers that spontaneously form the inverse hexagonal phase in the presence of water and can be photo-polymerized with retention of the overall microstructure (see view graphs enclosed). The result would be robust, crosslinked polymer networks with tunable, aligned, nanometer-scale channels of extremely uniform size.

- (e) Significant Results and Progress:

In the five month period between the termination of our first ONR grant (from which seed money was obtained to initially develop this membrane project) and the date of this report (one month into the current grant), significant progress has been made in pore size control and fabrication of the nanoporous networks into usable membrane films. Samples of these films have been submitted for study.

Previously, we reported demonstration of basic proof of concept for this project. Two novel amphiphilic monomers were synthesized that adopt the inverse hexagonal phase and can be photopolymerized with retention of the hexagonal channel architecture (Scheme 1). Preliminary experiments also showed that the channels in LC phases of monomer **1** can be homeotropically aligned in thin films using simple techniques. Over the past five months, we have managed to systematically alter the interchannel spacing (and implicitly, the channels diameter) of these nanoporous networks by exchanging the sodium counterion of the monomers with transition-metal and lanthanide ions. For example, the Ni(II), Co(II), Ce(III), and Eu(III) analogs of **1** all exhibit the inverse hexagonal LC phase, but with varying interchannel spacings in the 29–37 Å range. Photopolymerization of the LC phases of these monomers result in retention of the phase architecture and dimensions. The significance of this work is that a simple method can be used to control pore size in these nanoporous materials. The optical and magnetic properties of the transition-metals and lanthanide ions are apparently also incorporated into the resulting polymers, thus affording the potential more advanced membrane applications.

Transition-metal and lanthanide exchange in monomer **1** in general alter the processability of the resulting LC phase. For example, the Ni(II) and Co(II) analogs of **1** are much less viscous and pasty at ambient temperature than the sodium salt. They also can be processed to give

homeotropically aligned films at much lower temperatures. Polymer networks made with the Co(II) salt can be homeotropically aligned so well that polymerized films  $\geq 60 \mu\text{m}$  thick are optically transparent, yet are brown-colored and display the characteristic X-ray diffraction profile of a hexagonal phase, consistent with a monodomain sample. Polymer films of **1** and its Co(II) analog (approximately 1.5–2 cm in diameter) have just been submitted to Prof. B. Freeman at NCSU for quantitative determination of water uptake. (Preliminary experiments by the Freeman lab have demonstrated that earlier samples of polymerized **1** absorb water). Samples have also been submitted for BET gas absorption measurements in order to determine surface area.

## Description of Enclosed View Graphs and Slides

### View Graph # 1:

This view graph presents an overview of the rationale and accomplishments of our membranes research program over the past 5 months, from the termination of our last ONR grant (from which seed money was used to develop the membranes project) to one month after the start of the current grant. We have managed to not only provide proof of concept for the novel approach of constructing ordered nanoporous membranes using polymerizable amphiphilic LCs as building blocks, but we have also demonstrated control over pore dimensions and macroscopic sample alignment utilizing changes in molecular structure. Samples of aligned nanoporous films are currently under evaluation by collaborators.

### View Graph # 2:

This view graph shows x-ray diffraction evidence for the inverse hexagonal structure for one of primary monomer platforms, which contains long aqueous channels in a close-packed hexagonal arrangement. X-ray diffraction provides unequivocal confirmation for this nano-architecture, since LC phases with other geometries have characteristically different X-ray diffraction peaks. The graph shows that the LC monomer phase with the composition specified above has an interchannel spacing of approximately 4 nm (i.e.,  $d_{100}/\cos 30^\circ$ ) at ambient temperature. After one hour of photopolymerization with 365 nm light ( $1800 \mu\text{W}/\text{cm}^2$ ) at ambient temperature, the resulting insoluble, crosslinked film exhibits the same characteristic X-ray diffraction profile, except that the unit cell dimensions have decreased slightly as would be expected upon crosslinking.

### View Graph # 3

This view graph provides X-ray diffraction data showing how the interpore spacing of the nanoporous networks can be changed upon exchange of the sodium cation on the headgroup with various transition-metal and lanthanide cations. Although not all transition-metal or lanthanide cation derivatives of **1** can form the inverse hexagonal phase at the system composition specified, one basic trend can be inferred from the small number of derivatives we have synthesized so far: More positively charged metal ions tend to decrease the interpore distance by drawing the anionic headgroups closer together.

### Photographic Slide:

This slide (should you choose to use it) shows what thin, polymerized and oriented films of monomer **1** and its Co(II) analog look like. Please note the transparency and uniformity of the samples and the fact that these films can be made in fairly large sizes. The film thickness of the two films shown are approximately 30  $\mu\text{m}$  for the colorless sodium salt (**1**) film and 60  $\mu\text{m}$  for the Co(II) salt film.

# Functionalized Nanoporous Polymer Membranes with Well-Defined Pore Architectures via Lyotropic Liquid-Crystalline Monomers


Douglas L. Gin, University of California at Berkeley

## Objectives:

- Develop superior polymer-based ultrafiltration and reverse osmosis membranes for water purification.

## Challenges:

- Current polymer membrane manufacturing technologies lack control over pore size pore density, channel orientation, and uniformity on the nm scale.
- Control over these parameters is crucial for UF & RO processes.

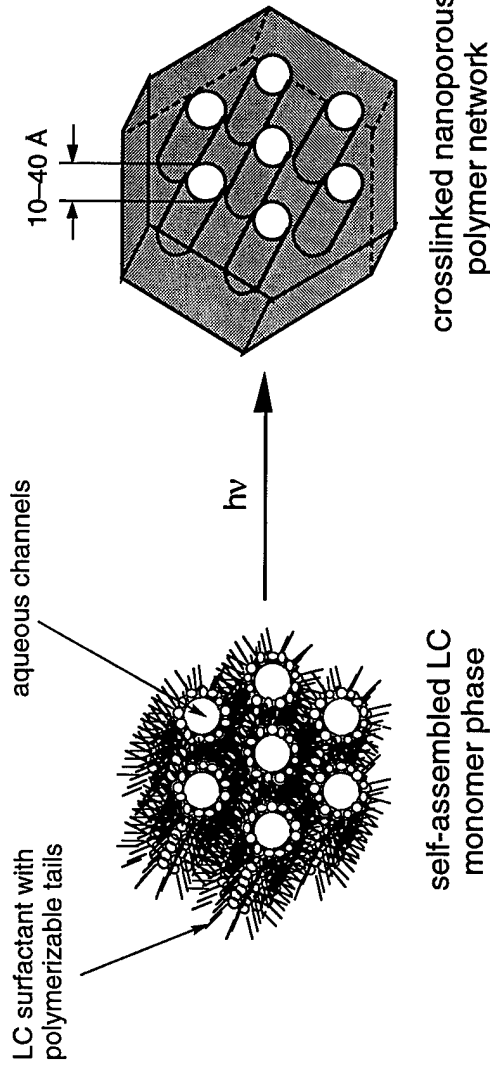

## Approach:

- Synthesis of ordered, nanoporous networks using self-assembly properties of polymerizable lyotropic liquid crystals (amphiphiles).
- Design and synthesis of polymerizable amphiphiles that form the inverse hexagonal phase and then photo-polymerize with retention of structure.
- Devise pore size tuning strategies based on molecular design.
- Develop pre-polymerization processing.

## Accomplishments:


- Developed 2 suitable lyotropic LC monomer platforms.
- Demonstrated proof of concept for construction of nanoporous polymer networks.
- Developed simple technique for formation of uniformly aligned thin films.
- Control of nm pore size and spacing via choice of metal cation on ionic headgroup.

## Transitions:

- Samples currently being studied by collaborators for water absorption and basic separation.
- Patent application on basic process filed on Jan. 8, 1997 as part of a broad patent.



# Low Angle X-Ray Diffraction Results for Lyotropic LC Monomer 1


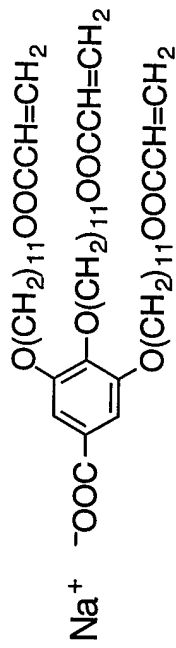


1


LC mixture: 85/10/5 (w/w/w)  
LC/H<sub>2</sub>O/initiator in xylene

Characteristic hexagonal peak spacing ratio:

1	$\frac{1}{\sqrt{3}}$	$d_{110}$	.....
1	$\frac{1}{\sqrt{4}}$	$d_{200}$	.....
1	$\frac{1}{\sqrt{7}}$	$d_{210}$	.....

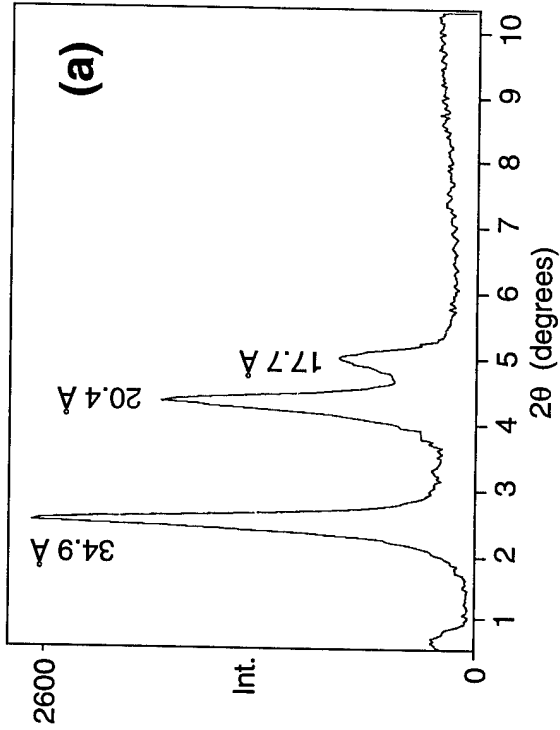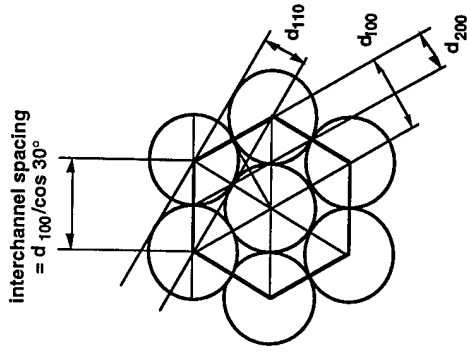


(a) Before polymerization

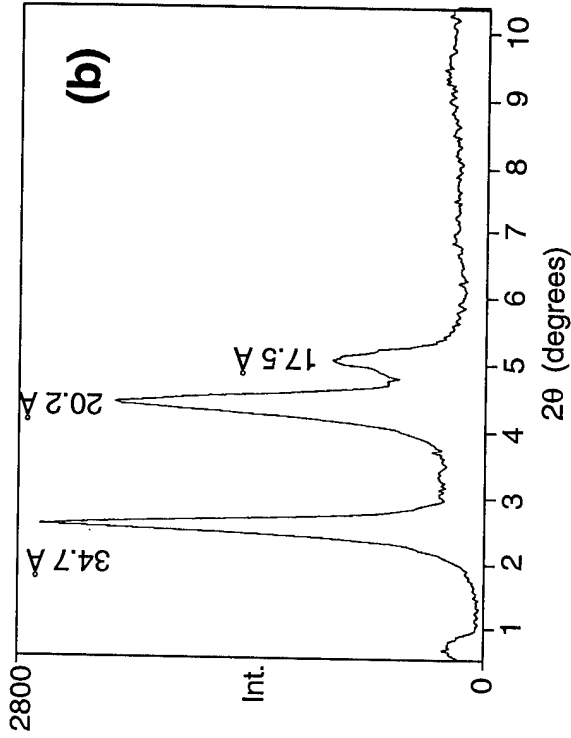

(b) After polymerization

## Modulation of Interpore Distances via Choice of Headgroup Counterion

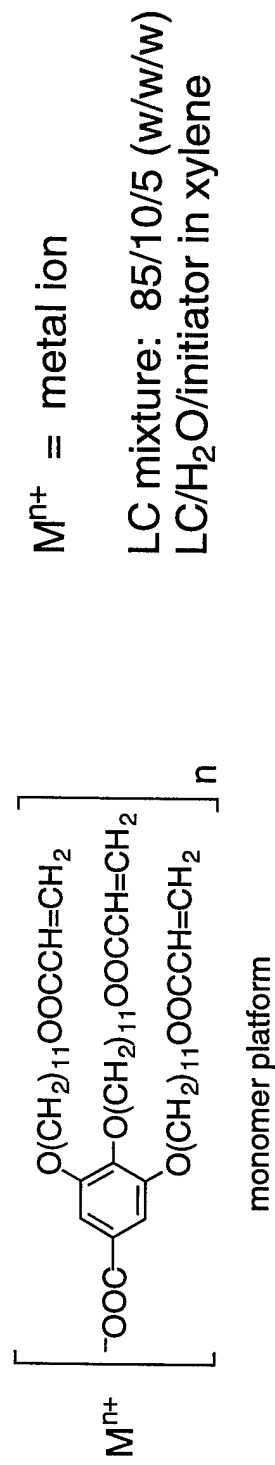

Metal Ion (radius, Å)	$d_{100}$ (Å)	$d_{110}$ ( $d_{100}/3^{1/2}$ ) (Å)	$d_{200}$ ( $d_{100}/2$ ) (Å)
Ni(II) (0.69)	36.65	21.08 (21.16)	18.44 (18.32)
After polymerization	35.75	20.83 (20.64)	18.19 (17.87)
Co(II) (0.72)	36.70	21.36 (21.16)	18.10 (18.35)
After polymerization	35.60	20.31 (20.55)	17.68 (17.80)
Ce(III) (1.07)	31.31	18.22 (18.08)	15.61 (15.65)
After polymerization	30.88	17.76 (17.83)	15.47 (15.44)
Eu(III) (0.95)	30.14	17.62 (17.40)	15.35 (15.07)
After polymerization	30.20	17.73 (17.44)	15.68 (15.10)