

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.

1. REPORT DATE (DD-MM-YYYY)		2. REPORT TYPE Technical Papers		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER 1011	
				5e. TASK NUMBER CA9F	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Air Force Research Laboratory (AFMC) AFRL/PRS 5 Pollux Drive Edwards AFB CA 93524-7048				8. PERFORMING ORGANIZATION REPORT	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Research Laboratory (AFMC) AFRL/PRS 5 Pollux Drive Edwards AFB CA 93524-7048				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S NUMBER(S)	
12. DISTRIBUTION / AVAILABILITY STATEMENT  Approved for public release; distribution unlimited.					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT  A	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON Leilani Richardson
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			

20030110 136

18 separate items enclosed

TP-1998-111

1011CRAT

99/31

MEMORANDUM FOR IN-HOUSE PUBLICATIONS

10 Jun 98

FROM: PROI (TI) (STINFO)

SUBJECT: Authorization for Release of Technical Information, Control Number: AFRL-PR-ED-TP-1998-111

Daniel Baron, Tim Miller, C.T. Liu "Subcritical Crack Growth in a Composite Solid Propellant"  
Journal Submission (Statement A)

## Subcritical Crack Growth in a Composite Solid Propellant

D.T. Baron  
Raytheon STX Corp.  
Edwards AFB, CA 93524

T.C. Miller  
Sparta Inc.  
Edwards AFB, CA 93524

C.T. Liu  
Air Force Research Laboratory  
Edwards AFB, CA 93524

### Abstract

Uniaxial tension tests using a strain rate of 0.04 in./in./min. are performed on rectangular smooth and single edge-notched specimens of varying thicknesses for a composite solid propellant. Stress-strain, crack growth, crack growth rate and crack growth resistance data are provided. Thickness effects and the mechanism of crack growth are described. Methods of calculation are explained for the crack growth rate and the Mode 1 stress intensity factor. A model is developed for the crack stable growth rate as a function of the stress intensity factor.

### Key Words

linear elastic fracture mechanics, LEFM, plane stress, composite solid propellant, crack growth, crack growth rate, mode 1 stress intensity factor, crack growth resistance curve, thickness effect.

### Introduction

Composite solid propellants consist of a lightly crosslinked polymer, highly filled with relatively coarse solid particles. Their loaded response is viscoelastic. Previous studies have been conducted to investigate crack growth in these materials {1-5}. The basic approach is based on linear elastic or linear viscoelastic fracture mechanics. Experimental results have shown that a power law relationship exists between the crack growth rate ( $\dot{a}$ ) and the Mode 1 (opening mode) stress intensity factor ( $K_1$ ). This is consistent with the linear viscoelastic fracture theories developed by Knauss {6} and Schapery {7}.

An example of a composite solid propellant can be described as follows {8}. Ammonium perchlorate crystal particles of two sizes, diameters  $20\mu$  ( $1\mu = 10^{-6}$  meter) and  $200\mu$  function as the oxidizer. The oxidizer weight fraction for the  $20\mu$  particles is 0.3. The oxidizer weight fraction for the  $200\mu$  particles is 0.7. Aluminum powder particles of diameter  $30\mu$  function as the fuel. Polybutadiene rubber functions as the matrix/binder (also as fuel). The weight fractions for the oxidizer, fuel, and matrix/binder are respectively 0.7, 0.2, 0.1. The specific gravities are respectively 1.69, 2.65, 1.0. The volume fractions are therefore respectively 0.7, 0.13, 0.17. The particle volume fraction (PVF) is 0.87. For every  $200\mu$  diameter particle, there are approximately 77  $30\mu$  diameter particles, and 429  $20\mu$  particles.

For this paper, four different thicknesses (0.2", 0.5", 1.0", 1.5") of smooth and single edge-notched tension (SENT) specimens of a composite solid propellant were uniaxially strained at a

**DISTRIBUTION STATEMENT A**  
Approved for Public Release  
Distribution Unlimited

rate ( $\dot{\epsilon}$ ) of 0.04 in./in./min. The induced end force ( $F$ ) and crack length ( $a$ ) (for the SENT specimens) were recorded as functions of  $\dot{\epsilon}$  (equivalently as functions of time,  $t$ ). Photographs showing the crack growth mechanism are included in the paper, and the mechanism is described. Stress ( $\sigma$ ) is plotted versus strain ( $\epsilon$ ) for both the smooth and notched specimens.  $\dot{a}$  is calculated, and  $a$  and  $\dot{a}$  are plotted versus  $t$ .  $K_1$  is calculated and plotted versus the change in the crack length ( $\delta a$ ), giving the material's crack growth resistance curve (R-curve). There are plots showing the relationship between  $\dot{a}$  and  $K_1$ . The  $\dot{a}(K_1)$  function is modeled and interpreted. Effects of specimen thickness ( $b$ ) are noted. Linear elastic fracture mechanics (LEFM) was used. For finite element calculations the state of plane stress was used for all thicknesses. This is because there was no consistent evidence of plane strain, even in the thickest (1.5") specimens, as will be reported.

### Experiments

All test specimens were rectangular, 1 in. wide ( $w = 1$  in., perpendicular to the direction of loading) and 5 in. long ( $h = 5$  in.). Specimen ends were glued to aluminum tabs and subjected to an applied uniform uniaxial displacement rate ( $\dot{\Delta}$ ) of 0.2 in./min. (applied uniform uniaxial nominal strain rate ( $\dot{\epsilon}$ ) of 0.04 in./in./min.). Four specimen thicknesses ( $b$ ) were used, 0.2 in., 0.5 in., 1.0 in., and 1.5 in. Eight unnotched specimens were tested, two of each thickness. The stress ( $\sigma$ ) vs. strain ( $\epsilon$ ) curves for those tests are shown in Figure 7. The average initial (linear) value ( $E_0$ ) for Young's Modulus is 734 psi. The average maximum stress ( $\sigma_{\max}$ ) is 90.9 psi, and the average strain at the maximum stress ( $\epsilon(\sigma_{\max})$ ) is 0.187. The average maximum strain ( $\epsilon_{\max}$ ) is 0.204. The overall trend is for ( $\epsilon_{\max}$ ) to decrease as  $b$  increases. Eight single edge-notched (SENT) specimens were tested (Mode I loading), two of each thickness. The notch length ( $a_0$ , cut along the specimen width) used was 0.3 in. The  $\sigma$  vs.  $\epsilon$  curves for those tests are shown in Figure 8. ( $\sigma$  is calculated using the specimen uncracked cross sectional area,  $A = bw$ ). The curves show small slopes near the origin. This is probably because the specimens were unintentionally put in an initial state of slight compression. The average value for  $\sigma_{\max}$  (calculated using  $A = bw$ ) is 40.6 psi. The average value for  $\epsilon(\sigma_{\max})$  is 0.075. The overall trend is for Young's Modulus ( $E$ ) and  $\sigma_{\max}$  to increase as  $b$  increases.

The plots of Figures 8-14 refer to the eight SENT specimens. In each plot the data shown for a particular specimen stops when failure begins, and therefore corresponds to the strain range  $0 \leq \epsilon \leq \epsilon(\sigma_{\max})$ . This is done so that LEFM can be used. LEFM is not valid once  $\sigma$  begins to decrease as a specimen fails.

### Crack Growth Mechanism

The largest particles in a composite solid propellant are typically larger than 100 $\mu$  (0.1 mm.), so at that scale these materials are non-homogeneous. When stretched, the variations in particle size, particle distribution, cross link density, and particle-binder bonds result in non-homogeneous

stresses and strengths. Because the particles can be considered rigid with respect to the polymer, the magnitudes of local stresses can be much greater than the magnitudes of the applied stresses, particularly when the gaps between particles are small. Because of the randomness of local stresses and strengths, local failure locations usually do not coincide with the points of maximum stress as determined from an elastic analysis for a homogeneous isotropic material. For a cracked specimen, a damage zone forms ahead of the crack tip. Local failures (voids or microcracks) usually occur first in the interior of the damage zone, not at the crack tip itself. The crack tip extends into the damage zone when the ligament of material separating it from the nearest void or microcrack breaks. The front of the void or microcrack becomes the new crack tip. As the crack tip extends, the damage zone moves forward, gaining new material. The type of damage which causes void formation is matrix/binder cracking. The types of damage which cause damage zone microcracking are particle-matrix/binder debonding (dewetting) and particle cracking.

Figures 1-6 show photographs of crack growth in the SENT specimens. All four specimen thicknesses (0.2", 0.5", 1.0", 1.5") are shown, and the common growth mechanism is void formation in the damage zone ahead of the crack tip, and then crack tip extension due to ligament rupture. This type of growth produces the rough crack surfaces shown in Figures 3-6. Figures 1 and 2 show crack initiation from an initial notch. Crack tip blunting occurs before initiation because of the large uniaxial strain (Figure 7) the material is capable of withstanding.

Examinations of the SENT specimen fracture surfaces showed, that for all thicknesses the crack fronts were straight lines and perpendicular to the direction of crack growth. This implies that the region near the crack tip always experienced a state of plane stress. If plane strain existed, it would have been indicated in the thicker specimens by a curved crack front which was advanced farther near its middle, and less near its edges. In that case the interior of the crack tip region would be in plane strain and the exterior would be in plane stress. (A material's crack growth resistance is less in plane strain than in plane stress). Apparently, void formations in the damage zone prevented the lateral constraint which is necessary for a state of plane strain.

#### Calculation of the Crack Growth Rate

The rates ( $\dot{a}$ ) of crack growth (for  $n + 1$  points ( $a, t$ ) numbered 0, 1, ...,  $n$ ) were calculated by

$$\begin{aligned}\dot{a}(0) &= \frac{a(1) - a(0)}{t(1) - t(0)} \\ \dot{a}(i) &= \max\left(\frac{a(i) - a(i-1)}{t(i) - t(i-1)}, \frac{a(i+1) - a(i)}{t(i+1) - t(i)}\right) \\ \dot{a}(n) &= \frac{a(n) - a(n-1)}{t(n) - t(n-1)}\end{aligned}\quad (1)$$

This method is easy to implement, and assigns each experimental point ( $a, t$ ) a value of  $\dot{a}$ . The values of  $\dot{a}$  are not smoothed. Each interior point ( $a, t$ ) is assigned the larger of the two adjacent calculated values. Using the method results in the ability to determine the most conservative upper bound on the envelope of  $\dot{a}$  for the set of SENT specimens.

### The Experimental Crack Growth Rate

Figure 9 shows a plot of crack length ( $a$ ) vs. time ( $t$ ). The crack initiation time ( $t_c$ ) varies from 1.34 min. to 1.59 min. The average value for  $t_c$  is 1.45 min. The corresponding applied nominal strain at crack initiation ( $\epsilon_c = t_c \cdot \dot{\epsilon}$ ) varies from 0.0535 to 0.0636. The average value for  $\epsilon_c$  is 0.0581. The maximum recorded value for  $a$  is 0.427 in. Figure 10 shows a plot of crack growth rate ( $\dot{a}$ ) vs. time. The maximum calculated value for  $\dot{a}$  is 0.847 in./min., approximately 4.2 times the applied displacement rate of  $\dot{\Delta} = 0.2$  in./min.

### Calculation of the Mode I Stress Intensity Factor

For the SENT experiments, a specimen's edge displacement ( $\Delta$ ) was prescribed as a function of time ( $t$ ). The crack length ( $a$ ), was measured as a function of  $t$ . For each point ( $\Delta, a$ ) of each specimen thickness ( $b$ ), the LFM Mode I stress intensity factor ( $K_1$ ) was calculated by the method described in this section.

$K_1$  can be written in the form

$$K_1 = \sigma_{\text{avg.}} \sqrt{w} f\left(\frac{a}{w}, \frac{h}{w}\right), \quad (2)$$

where  $\sigma_{\text{avg.}}$  is the average value for  $\sigma$ ,  $w$  is the specimen width,  $h$  is the specimen length, and  $f$  is some function of  $a/h$  and  $h/w$ . Dividing  $K_1$  by  $\sigma_{\text{avg.}} \sqrt{a}$  gives

$$\frac{K_1}{\sigma_{\text{avg.}} \sqrt{a}} = \sqrt{\frac{w}{a}} f\left(\frac{a}{w}, \frac{h}{w}\right) = g\left(\frac{a}{w}, \frac{h}{w}\right), \quad (3)$$

where  $g$  is a second function of  $a/h$  and  $h/w$ . According to LFM, the energy release rate ( $J$ ) can be expressed as

$$J = \frac{K_1^2}{E}, \quad (4)$$

where  $E$  is Young's Modulus. This implies that

$$K_1 = \sqrt{JE}. \quad (5)$$

$\sigma_{\text{avg.}}$  can be expressed as

$$\sigma_{\text{avg.}} = \frac{F}{A}, \quad (6)$$

where  $F$  is the end force induced on the specimen, and  $A$  is the specimen's uncracked cross-sectional area ( $bw$ ). Therefore  $\sigma_{\text{avg.}}$  becomes

$$\sigma_{\text{avg.}} = \frac{F}{bw}. \quad (7)$$

Using Equations 5 and 7 in Equation 3 gives

$$\frac{K_1}{\sigma_{\text{avg.}} \sqrt{a}} = g\left(\frac{a}{w}, \frac{h}{w}\right) = \frac{bw}{F} \sqrt{\frac{JE}{a}}. \quad (8)$$

The function  $g\left(\frac{a}{w}, \frac{h}{w}\right)$  is the specimen geometry correction factor for stress intensity, and is approximated by numerically calculating  $\frac{bw}{F} \sqrt{\frac{JE}{a}}$ . Linear elastic plane stress finite element calculations (ABAQUS code) were performed of a SENT specimen subjected to a uniform uniaxial displacement ( $\Delta$ ), using  $w = 1$  and  $h = 5$ . The value of the specimen thickness ( $b$ ) does not appear in plane finite element calculations, and is implicitly equal to 1. (Note that the value of  $g$  is independent of the value of the prescribed displacement ( $\Delta$ ) used in a finite element calculation. Note also that although  $E$  appears in the expression  $\left(\frac{bw}{F} \sqrt{\frac{JE}{a}}\right)$  for  $g$ , the value of the expression is independent of the value of  $E$  used. Any (positive) values can be used for  $\Delta$  and  $E$  in the finite element calculations. The value of  $g$  depends only on the two parameters  $a/w$  and  $h/w$ .) The value of  $a$  was varied, and one finite element calculation was performed for each value. Each finite element calculation output a value for  $F$  and a value for  $J$  (energy domain integral method).  $g$  was plotted versus  $a/w$ . A second order polynomial was fitted to  $g$ ,

$$g\left(\frac{a}{w}, \frac{h}{w} = 5\right) \cong p_0 + p_1 \frac{a}{w} + p_2 \left(\frac{a}{w}\right)^2, \quad (9)$$

giving a close approximation to the function. From Equation 8,

$$K_1(\Delta, a, b, w, h) = \sigma_{\text{avg.}} \sqrt{a} \cdot g\left(\frac{a}{w}, \frac{h}{w}\right). \quad (10)$$

Using Equations 7 and 9 in Equation 10 gives

$$K_1(\Delta, a, b, w, h = 5) = \frac{F\sqrt{a}}{bw} \cdot \left( p_0 + p_1 \frac{a}{w} + p_2 \left( \frac{a}{w} \right)^2 \right). \quad (11)$$

For each experimental point  $(\Delta, a)$  of each specimen thickness  $(b)$ ,  $K_1(\Delta, a, b, w = 1)$  was determined using Equation 11, in which  $F$  was the experimentally measured specimen end force associated with  $(\Delta, a)$ .

The alternative "brute force" method for calculating  $K_1$  is to make one finite element calculation for each experimental point  $(\Delta, a)$  of each specimen thickness  $(b)$ , in order to find  $J$  for the point, and then to compute  $K_1$  with Equation 5, using  $E = E_0$ . The advantage of using the method of this section is that once the approximating function of Equation 9 is determined,  $K_1$  can be found for any number of points  $(\Delta, a)$  without doing more finite element calculations. Each finite element calculation of  $J$  is not trivial with respect to the number of elements required to obtain a reasonably accurate result. When determining the function  $g$  of Equation 8, only enough points were (finite element) calculated to provide the function's shape.

(There is a standard equation for the determination of  $K_1$  in a SENT specimen. It is only valid when  $h/w$  is "large". "Large" for a specimen with a prescribed displacement is much larger than the case for this paper,  $h/w = 5$ .)

### The Crack Growth Resistance Curve

Figure 11 is a plot of  $K_1$  vs. the change in the crack length  $(\delta a)$ . These curves are called crack growth resistance curves (R-curves), and are a measure of a material's resistance to crack growth. The average value of  $K_1$  at crack initiation ( $K_{1c}$ ) is  $47.8 \text{ lb.} \div \text{in.}^{1.5}$ . The maximum value recorded for  $K_1$  is  $81.4 \text{ lb.} \div \text{in.}^{1.5}$ . The condition  $K_1 < K_{1c}$  corresponds to crack tip blunting, as is shown in Figure 1. The overall trend is for  $K_{1c}$  to increase with increasing  $b$ . (This trend provides additional evidence that the thicker specimens were not in a state of plane strain. If it is assumed that as a specimen's thickness  $(b)$  is increased, the state of the crack tip region transitions from plane stress to plane strain, then  $K_{1c}$  should decrease with increasing  $b$ , because a material's crack growth resistance is smaller in plane strain than in plane stress.)

### Analysis of the Crack Growth Rate

Figure 12 shows a plot of  $\dot{a}$  vs.  $K_1$ . The distribution of the points suggest the use of a parabolic modeling function. According to Knauss {6}, and Schapery {7}, the crack growth rate for a SENT specimen of a linearly viscoelastic material can be expressed as

$$\dot{a} = c_1 K_1^{c_2}. \quad (12)$$



(Note that in Equation 12,  $c_1$  and  $c_2$  are not asserted to be material properties, but rather are assumed to be specimen dependent.) Therefore,

$$\log_{10}(\dot{a}) = \log_{10}(c_1) + c_2 \log_{10}(K_1). \quad (13)$$

Figure 13 shows a plot of  $\log_{10}(\dot{a})$  vs.  $\log_{10}(K_1)$ . Also shown is a least squares linear curve fit, giving (for  $[\dot{a}] = \text{in.} \div \text{min.}$ ,  $[K_1] = \text{lb.} \div \text{in.}^{1.5}$ , ( $[x] \equiv \text{"units of } x\text{"}$ ))

$$\log_{10}(\dot{a}) = -4.58 + 2.26 \log_{10}(K_1). \quad (14)$$

Therefore, the best fit pair  $(c_1, c_2)$  for representing all eight SENT specimens is  $(10^{-4.58}, 2.26)$ . Equation 12 can then be written

$$\dot{a} = 2.63 \times 10^{-5} K_1^{2.26} \text{ in./min.} \quad (15)$$

It was observed that  $c_1$  and  $c_2$  are not independent parameters. Figure 14 shows a plot of  $\log_{10}(c_1)$  vs.  $c_2$  (one best fit pair  $(c_1, c_2)$  is calculated for each of the eight SENT specimens). Also shown is a least squares linear curve fit, giving,

$$\log_{10}(c_1) = -0.553 - 1.79c_2. \quad (16)$$

Substituting Equation 16 into Equation 12 eliminates  $c_1$  and gives

$$\dot{a} = 0.280 \cdot (0.0164K_1)^{c_2} \text{ in./min.} \quad (17)$$

$c_2$  can be solved for, giving

$$c_2 = \frac{\log_{10}(\dot{a}) + 0.554}{\log_{10}(K_1) - 1.79}. \quad (18)$$

Equation 18 indicates that for a particular SENT specimen, any experimental point  $(K_1, \dot{a})$  should give an estimate for the parameter  $c_2$  for that specimen.

Substituting Equation 16 into Equation 13 and rearranging gives

$$\log_{10}(\dot{a}) + 0.553 = c_2 \cdot (\log_{10}(K_1) - 1.79). \quad (19)$$

Equation 19 has the form of a line, i.e.,

$$y - y_1 = m \cdot (x - x_1). \quad (20)$$

Therefore, Equation 16 is identically satisfied for any line which passes thru the point  $(\log_{10}(K_1) = 1.79, \log_{10}(\dot{a}) = -0.553)$ , and has some slope  $c_2$ . This means any line passing thru the point  $(1.79, -0.553)$ . If Equation 16 was exactly true (if each point in Figure 14 was exactly on the line), then in Figure 13 the shown line (which is the best fit for the aggregate of the specimens) would pass thru the point  $(1.79, -0.553)$ . Also if Equation 16 was exactly true, then in Figure 13 if a best fit line was plotted for each specimen, all of those lines would pass thru the point  $(1.79, -0.553)$ . Therefore, point  $(1.79, -0.553)$  can be designated the "pivot point" for line fits of specimen experimental data of  $\log_{10}(\dot{a})$  vs.  $\log_{10}(K_1)$ .

Each point  $(\log_{10}(c_1), c_2)$  in Figure 14 was determined by calculating a best fit line thru the points  $(\log_{10}(K_1), \log_{10}(\dot{a}))$  for the particular specimen. Then the relation of Equation 16 was determined by calculating a best fit line thru all of the points  $(\log_{10}(c_1), c_2)$ . The relation of Equation 14 was determined by calculating a best fit line thru the points  $(\log_{10}(K_1), \log_{10}(\dot{a}))$  for all of the specimens together. From Equation 14,  $\log_{10}(c_1) = -4.58$ . If  $c_2$  from Equation 14 ( $c_2 = 2.26$ ) is substituted into Equation 16, then  $\log_{10}(c_1) = -4.60$ . The two values of  $\log_{10}(c_1)$  vary by 0.4%. Their agreement is good because each point in Figure 14 is close to the fit line.

Equation 17 can be written in the form

$$\dot{a} = c_3 \cdot (c_4 K_1)^{c_2} \text{ in./min.}, \quad (21)$$

with  $c_3 = 0.280$  and  $c_4 = 0.0164$ .  $c_3$  and  $c_4$  are independent of specimen thickness ( $b$ ), and are constants for this particular composite solid propellant, and the particular values for the specimen width ( $w = 1$  in.), specimen length ( $h = 5$  in.), notch length (or initial crack length,  $a_0 = 0.3$  in.), and applied strain rate ( $\dot{\epsilon} = 0.04$  in./in./min.).  $c_2$  is a variable, dependent on the specific randomness of a particular specimen. Equation 21 is only approximately true, because Equation 16 is only approximately true. For any value of  $c_2$ , a curve having the form of Equation 21 will pass thru the common intersection point  $\left(K_1 = \frac{1}{c_4}, \dot{a} = c_3\right)$ . The common intersection point for best fit (to determine  $c_2$ ) curves of each of the eight SENT specimens represented in Figure 12 would be  $(K_1 = 61.0 \text{ lb.} \div \text{in.}^{1.5}, \dot{a} = 0.280 \text{ in./min.})$ . The physical meaning of having an approximate common intersection point for curves of  $\dot{a}$  versus  $K_1$  is that once crack

growth begins, the acceleration of the crack tip ( $\ddot{a}$ ) is proportional to the value of  $K_1$  when crack growth begins (proportional to the value of  $K_{1c}$ ). (Equivalently,  $\ddot{a}$  is proportional to the strain energy ( $U$ ) stored in the specimen when crack growth begins. This is intuitively logical. It is similar to the acceleration of a released spring being proportional to its initial compression.) The idea can be demonstrated using two extreme cases. A hypothetical best fit curve in Figure 12 with the exponent (from Equation 17)  $c_2 = 0$  would be a horizontal line thru the common intersection point. Then crack growth would begin at  $t = 0$  when  $K_1 = K_{1c} = 0$ , and would be constant with  $\dot{a} = 0.280$  in./min., and  $\ddot{a} = 0$ . A hypothetical best fit curve in Figure 12 with the exponent  $c_2 = \infty$  would give  $\dot{a} = 0$  for  $0 \leq K_1 < 61.0$  lb.  $\div$  in.<sup>1.5</sup>, jump to  $\dot{a} = 1.00$  in./min. for  $K_1 = 61.0$  lb.  $\div$  in.<sup>1.5</sup>, then jump to  $\dot{a} = \infty$  for  $K_1 > 61.0$  lb.  $\div$  in.<sup>1.5</sup>. Therefore there would be no crack growth until  $K_1 = K_{1c} = 61.0$  lb.  $\div$  in.<sup>1.5</sup>, when  $\ddot{a} \rightarrow \infty$ , and when specimen failure would be instantaneous.

### Conclusions

Constant uniaxial strain rate tests were performed on four thicknesses (0.2", 0.5", 1.0", 1.5") of specimens of a particular composite solid propellant. Tests were performed on eight smooth (unnotched) specimens to determine the material's uniaxial stress-strain behavior. Tests were performed on eight single edge-notched tension (SENT) specimens to determine cracked uniaxial stress-strain behavior, the material's Mode 1 crack growth resistance, and to determine and model the crack growth rate ( $\dot{a}$ ). Methods were described for calculating  $\dot{a}$  from crack growth data, and for calculating the Mode 1 stress intensity factor ( $K_1$ ). For all analysis, linear elastic fracture mechanics (LEFM) was used. Results showed that there were no consistent and significant effects of specimen thickness ( $b$ ). The crack growth data made it seem likely that for all four values of  $b$ , the crack tip region experienced a state of plane stress. This was explained as being due to void formations in the crack tip damage zone preventing the lateral constraint which would otherwise produce a state of plane strain in a thicker specimen. The crack growth rate was modeled as  $\dot{a} = c_1 K_1^{c_2}$ .  $c_1$  and  $c_2$  were assumed to be mutually independent of each other, and to individually depend on the specific randomness of a particular specimen. Then data showed that  $c_1$  and  $c_2$  were mutually dependent, and one could be eliminated. The crack growth rate could then be modeled as  $\dot{a} = c_3 \cdot (c_4 K_1)^{c_2}$ .  $c_3$  and  $c_4$  were independent of  $b$ , and depended on the particular material, and the particular values for the specimen width ( $w = 1$  in.), specimen length ( $h = 5$  in.), notch length ( $a_0 = 0.3$  in.), and applied strain rate ( $\dot{\epsilon} = 0.04$  in./in./min.). So  $c_3$  and  $c_4$  were constants for the eight SENT specimens.  $c_2$  depended on the specific randomness of a particular specimen. It was noted that all SENT specimen curve fits (to determine  $c_2$ ) of  $\dot{a} = c_3 \cdot (c_4 K_1)^{c_2}$  would pass thru the common point ( $K_1 = 1/c_4$ ,  $\dot{a} = c_3$ ). This implied that the acceleration of the crack tip ( $\ddot{a}$ ) during crack growth, was proportional to the value of  $K_1$  at

crack initiation (the value of  $K_{1c}$ ), and therefore proportional to the magnitude ( $U$ ) of the specimen's strain energy at crack initiation. This implication was proposed to be consistent with common experience.

### References

- {1} Liu, C.T., 'Crack growth behavior in a composite propellant with strain gradients - Part II', *Journal of Spacecraft and Rockets*, 27, 1990, 647-652.
- {2} Liu, C.T., 'Crack propagation in a composite solid propellant', *Proceedings of the 1990 SEM Spring Conference*, Baltimore MD, 1990, 614-620.
- {3} Smith, C.W., L. Wang, H. Mouille, and C.T. Liu, 'Near tip behavior of a particulate composite material containing cracks at ambient and elevated temperatures', *ASTM STP 1189*, 1993, 775-787.
- {4} Liu, C.T. and C.W. Smith, 'Temperature and rate effects on stable crack growth in a particulate composite material', *Proceedings of the 1994 SEM Spring Conference*, Baltimore MD, 1994, 146-149.
- {5} Liu, C.T., 'Numerical modeling of crack-defect interaction', *Journal of Propulsion and Power*, 7, 1991, 526-530.
- {6} Knauss, W.G., 'On the steady propagation of a crack in a viscoelastic sheet: Experiments and analysis', *Deformation and Fracture of High Polymers*, H. Henning Kausch, J.A. Hassell and R.I. Jaffee (eds.), Plenum Press, New York, 1974, 501-541.
- {7} Schapery, R.A., 'A theory of crack initiation and growth in viscoelastic media I', *International Journal of Fracture Mechanics*, 11, 1975, 141-159.
- {8} Sutton, G.P., *Rocket Propulsion Elements - An Introduction to the Engineering of Rockets*, 5th ed., John Wiley & Sons, New York, 1986, 292-316.

○	b = 0.2"
×	b = 0.2"
+	b = 0.5"
*	b = 0.5"
□	b = 1.0"
◇	b = 1.0"
▽	b = 1.5"
△	b = 1.5"
(b ≡ specimen thickness)	
LEGEND	
Figures 7-14	

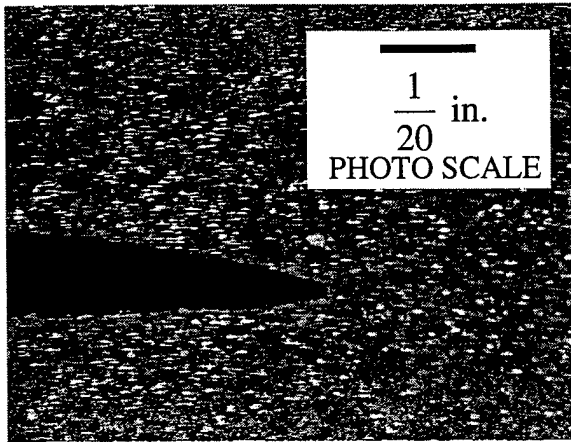


Figure 1.  $b = 1.0$  in., Crack Tip Blunting

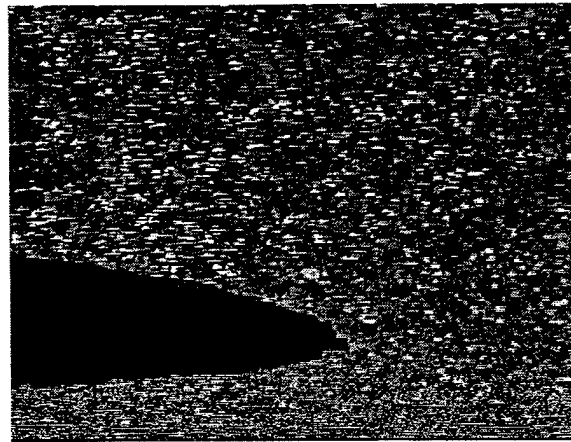


Figure 2.  $b = 1.0$  in., Initial Crack Growth

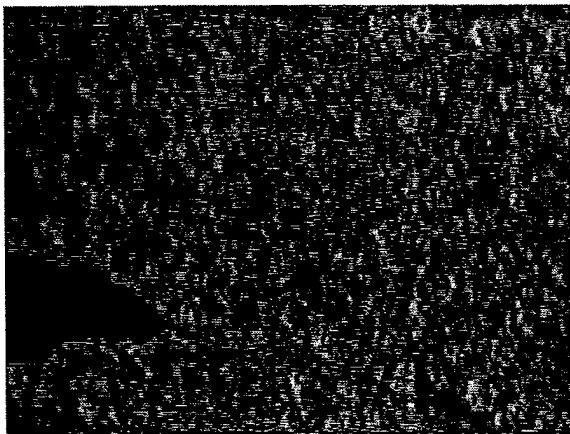


Figure 3.  $b = 1.5$  in., Damage Formation

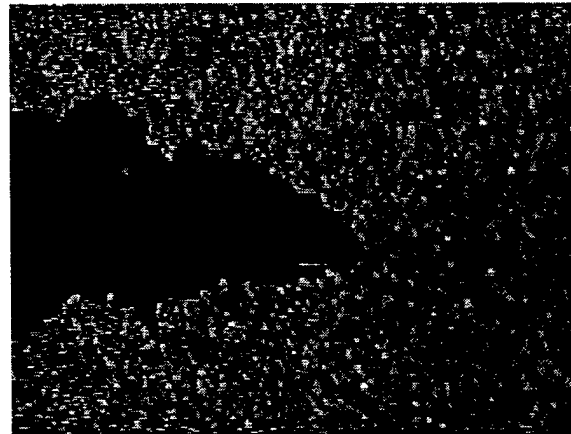


Figure 4.  $b = 0.2$  in., Damage Zone Voids

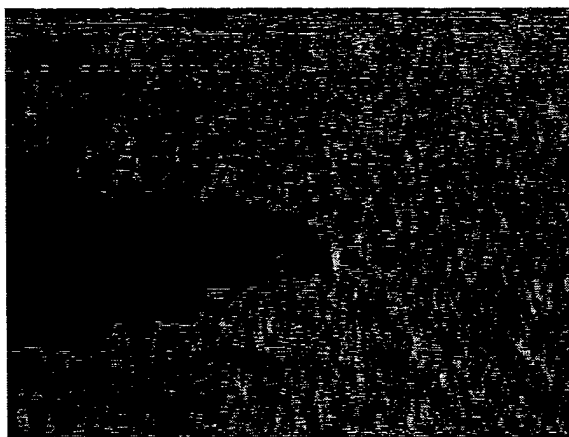


Figure 5.  $b = 0.2$  in., Single Ligament

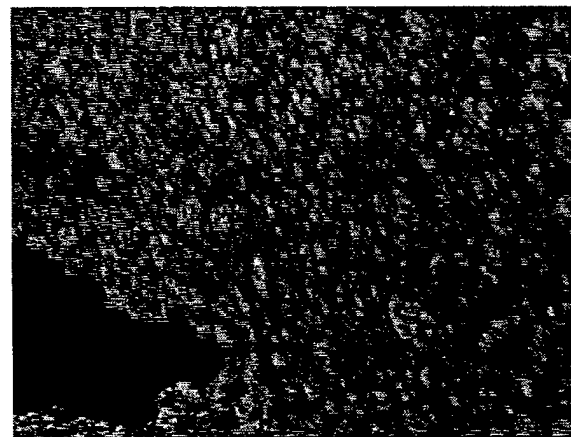


Figure 6.  $b = 0.5$  in., Double Ligament

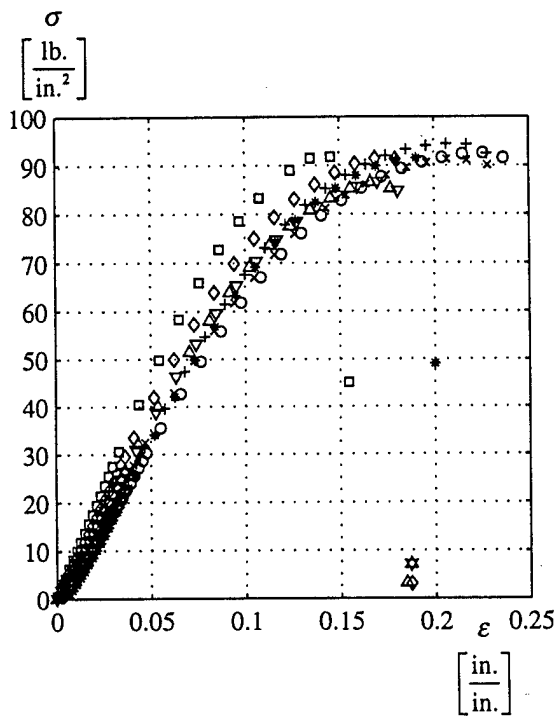


Figure 7.  $\sigma$  vs.  $\epsilon$ , Uncracked Specimens ( $a_0 = 0$ )

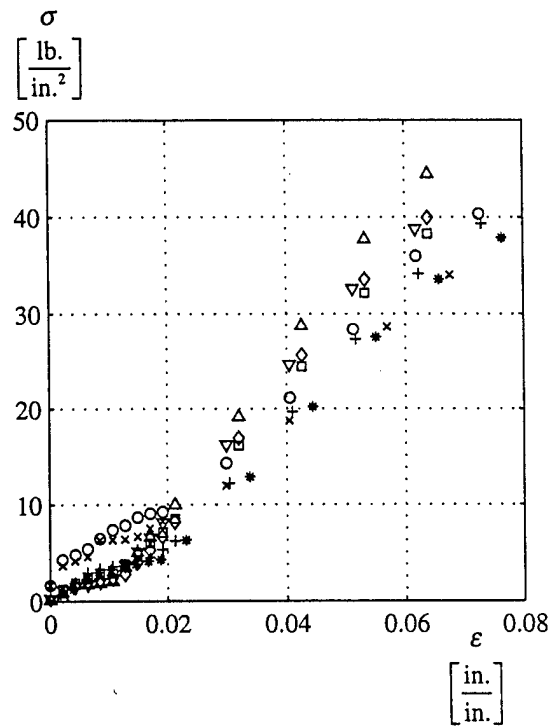


Figure 8.  $\sigma$  vs.  $\epsilon$ , Cracked Specimens ( $a_0 = 0.3$  in.)

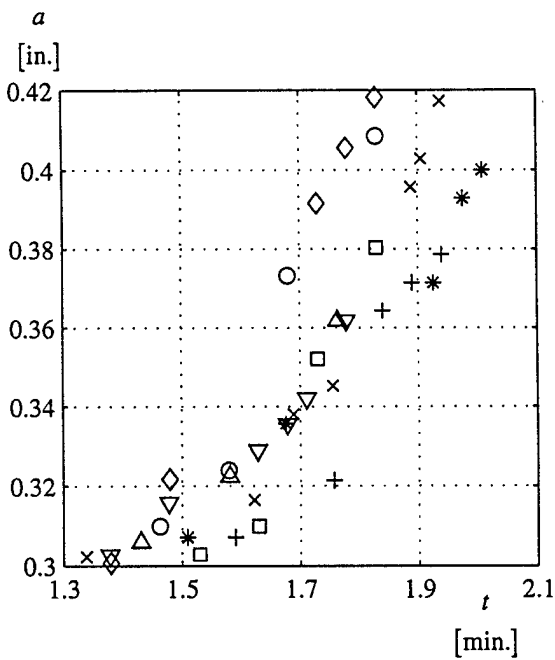


Figure 9.  $a$  vs.  $t$

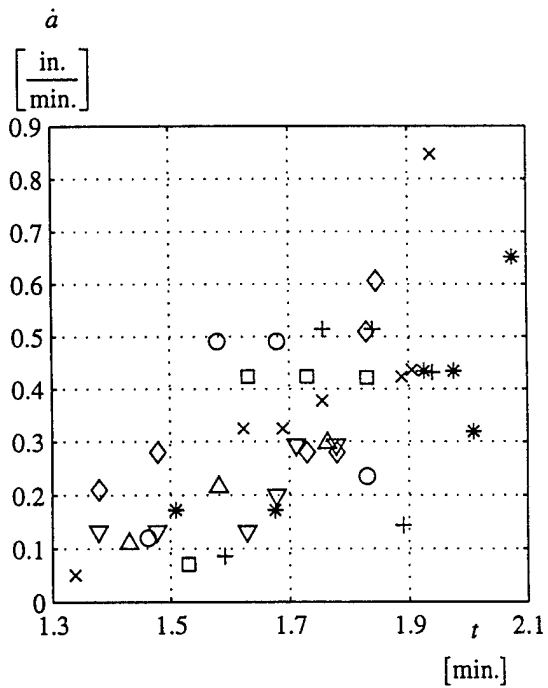


Figure 10.  $\dot{a}$  vs.  $t$

