

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. **PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**

|  |                             |                                    |                                     |                                   |  |
|--|-----------------------------|------------------------------------|-------------------------------------|-----------------------------------|--|
| 1. REPORT DATE (DD-MM-YYYY)  |                             | 2. REPORT TYPE<br>Technical Papers |                                     | 3. DATES COVERED (From - To)      |  |
| 4. TITLE AND SUBTITLE  |                             |                                    |                                     | 5a. CONTRACT NUMBER               |  |
|  |                             |                                    |                                     | 5b. GRANT NUMBER                  |  |
|  |                             |                                    |                                     | 5c. PROGRAM ELEMENT NUMBER        |  |
| 6. AUTHOR(S)   |                             |                                    |                                     | 5d. PROJECT NUMBER<br>1011        |  |
|  |                             |                                    |                                     | 5e. TASK NUMBER<br>CA9F           |  |
|  |                             |                                    |                                     | 5f. WORK UNIT NUMBER              |  |
| 7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)<br>Air Force Research Laboratory (AFMC)<br>AFRL/PRS<br>5 Pollux Drive<br>Edwards AFB CA 93524-7048        |                             |                                    |                                     | 8. PERFORMING ORGANIZATION REPORT |  |
| 9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)<br>Air Force Research Laboratory (AFMC)<br>AFRL/PRS<br>5 Pollux Drive<br>Edwards AFB CA 93524-7048 |                             |                                    |                                     | 10. SPONSOR/MONITOR'S ACRONYM(S)  |  |
|  |                             |                                    |                                     | 11. SPONSOR/MONITOR'S NUMBER(S)   |  |
| 12. DISTRIBUTION / AVAILABILITY STATEMENT<br><br>Approved for public release; distribution unlimited.  |                             |                                    |                                     |                                   |  |
| 13. SUPPLEMENTARY NOTES  |                             |                                    |                                     |                                   |  |
| 14. ABSTRACT   |                             |                                    |                                     |                                   |  |
| 20030110 128   |                             |                                    |                                     |                                   |  |
| 15. SUBJECT TERMS  |                             |                                    |                                     |                                   |  |
| 16. SECURITY CLASSIFICATION OF:  |                             |                                    | 17. LIMITATION OF ABSTRACT<br><br>A | 18. NUMBER OF PAGES               | 19a. NAME OF RESPONSIBLE PERSON                                |
| a. REPORT<br>Unclassified  | b. ABSTRACT<br>Unclassified | c. THIS PAGE<br>Unclassified       |                                     |                                   | Leilani Richardson   |
|  |                             |                                    |                                     |                                   | 19b. TELEPHONE NUMBER<br>(include area code)<br>(661) 275-5015 |

18 separate items enclosed

10/1/99

TP-FY99-0073

✓ Spreadsheet  
✓ DT3

MEMORANDUM FOR PRR (<sup>In House</sup> Contractor Publication)

FROM: PROI (TI) (STINFO)

5 April 1999

SUBJECT: Authorization for Release of Technical Information, Control Number: AFRL-PR-ED-TP-FY99-0073  
Tim Miller, "Overdeterministic Fracture Analysis and Singular Value Decomposition"

SEM Spring Conference

(Statement A)

# Overdeterministic Fracture Analysis and Singular Value Decomposition

Timothy C. Miller

Research Engineer, Air Force Research Laboratory, AFRL/PRSM, 10 E. Saturn Blvd., Edwards AFB, CA USA 93524

Ravinder Chona

Assoc. Professor, Texas A&M University, Dept. of Mechanical Engineering, College Station, TX USA 77843-3123

## INTRODUCTION

Using overdeterministic analysis to determine fracture parameters leads to unstable solutions in some cases because of ill-conditioning problems. The problem arises because some of the functions that constitute the overall field expressions are similar. In these cases, the solution is best obtained using singular value decomposition, which solves for the coefficients effectively even when ill-conditioning is present, and quantifies the condition of the matrix. The method is explained and its use is demonstrated with two sets of results for interfacial cracks in thermally loaded bimaterials.

## DEVELOPMENT

In a homogeneous, linear elastic, isotropic material, the horizontal component of displacement in a cracked body under mode I loading can be expressed as an infinite series: [1]

$$L(r, \theta) = u_x = \frac{1}{E} \sum_{n=0}^{\infty} C_{2n} \frac{r^{n+1/2}}{n+1/2} \{ (1-\nu) \cos[(n+1/2)\theta] - (1+\nu)(n+1/2) \sin(\theta) \sin[(n+1/2)\theta] \} + C_{2n+1} \frac{r^{n+1}}{n+1} \{ 2 \cos[(n+1)\theta] - (1+\nu)(n+1) \sin(n\theta) \sin(\theta) \} \quad (1)$$

Here  $E$  is Young's modulus,  $u_x$  is the horizontal displacement component,  $r$  and  $\theta$  are polar coordinates, and  $\nu$  is Poisson's ratio. Methods such as the local collocation method or the boundary collocation method require the truncation of this expression to a finite size. The researcher then measures the left-hand side of eq. (1) at  $m$  discrete points, yielding an overdetermined system that can be solved for the  $n$  unknowns by assuming random measurement errors and formulating this least-squares using linear algebra. [2]

One possible difficulty lies with the experimental data. A moiré method, for example, measures overall displacements, which, in addition to the crack-induced displacement component of eq. (1), includes a displacement component related to translation and rotation of the body about some point: [1]

$$M(r, \theta) = Pr \cos(\theta) + Qr \sin(\theta) + R \quad (2)$$

The parameters  $P$ ,  $Q$ , and  $R$  must also be treated as unknowns so the actual field equation used in the overdeterministic method is a combination of eqs. (1) and (2): [1]

$$N(r, \theta) = L(r, \theta) + M(r, \theta) \quad (3)$$

Trying to use linear algebra to solve this equation will give poor results unless the researcher realizes that the  $P$  term in eq. (2) and the  $C_1$  term in eq. (1) are linearly dependent terms. The two terms can be combined so that a nonsingular matrix is formed. Such a linear dependence will be manifested as a singular matrix. A similar situation occurs with the  $Q$  term when  $u_y$  fields are measured.

In the case of an interfacial crack lying between two materials, a field expression similar to eq. (1) exists, but is much more complicated because the solution for the bimaterial problem has complex eigenvalues. [3] The imaginary part of these eigenvalues is denoted  $\epsilon$  and is called the *bimaterial parameter*. The value for the bimaterial parameter depends on the stress state (plane stress or plane strain) and the material properties on each side of the crack. The crack induced fields can be expressed as: [4]

$$L(r, \theta) = \frac{1}{2\mu_1} [ a_{0r} r^{1/2} (f_{0r})_1 - a_{0j} r^{1/2} (f_{0j})_1 + b_{0r} r (g_{0r})_1 - b_{0j} r (g_{0j})_1 ] \quad y \geq 0 + \frac{1}{2\mu_2} [ a_{0r} r^{1/2} (f_{0r})_2 - a_{0j} r^{1/2} (f_{0j})_2 + b_{0r} r (g_{0r})_2 - b_{0j} r (g_{0j})_2 ] \quad y < 0 \quad (4)$$

Here  $\mu_1$  and  $\mu_2$  are the two shear moduli. The actual expression is an infinite series but for simplification has been truncated here. The terms with the  $r^{1/2}$  dependencies are associated with the complex stress intensity factor, and those linear in  $r$  with constant stress terms. The functions  $f$  and  $g$  shown in eq. (4) depend on the polar coordinate  $\theta$ , the material properties, and  $\epsilon$ .

One might expect that the combination of rigid body motion and crack induced displacement components would again give two linearly dependent terms, resulting in a singular matrix. However, due to the presence of the bimaterial parameter, these terms are *almost*, but not quite, linearly dependent. In the limit as  $\epsilon$  goes to zero, the matrix becomes singular, and the condition number approaches infinity. [4] For most

combinations of materials, however,  $\epsilon$  is small (on the order of 0.01 - 0.10) resulting in a nonsingular but ill-conditioned matrix.

Ill-conditioning of the matrix for interfacial fracture problems can then come from two sources: (i) the presence of similar (but not identical) terms when combining eqs. (2) and (4) and (ii) the errors introduced by lack of computational precision. Ill-conditioning caused by precision errors can sometimes be improved by the use of double precision numbers, but the similar terms in the field expression are an inherent feature. Worse yet, a researcher unaware of the ill-conditioning can still obtain a solution, and it may appear to be correct. The unstable solution is manifested by sporadic changes in the values for the determined parameters as the size of the truncated series is changed. [5]

A resolution is to use a more robust solution method. Linear algebra methods such as Gauss-Jordan elimination, Gaussian elimination with partial pivoting, and the Gauss-Seidel iterative technique have frequently been used with homogenous cracked bodies. Regardless of which of these is used, the design matrix,  $[f]$ , is formed from the functions in the combined expression and depends on the measured locations of the experimental data points. The vector of displacement component measurements,  $\{N\}$ , and the vector of unknown parameters,  $\{C\}$ , relate to  $[f]$  through:

$$\begin{matrix} \{N\} = [f] \{C\} \\ mx1 \quad mxn \quad nx1 \end{matrix} \quad (5)$$

The conventional matrix approach proceeds by premultiplication with the transpose of  $[f]$  to produce a square matrix,  $[a]$ , which is then solved using one of these techniques [2]:

$$\begin{aligned} [f]^T \{N\} &= [f]^T [f] \{C\} \\ \text{Let } \{d\} &= [f]^T \{N\}, \quad [a] = [f]^T [f] \\ \{d\} &= [a] \{C\} \\ nx1 \quad nxn \quad nx1 \end{aligned} \quad (6)$$

Attempts to apply this algorithm to the interfacial problems results in unstable solutions. A preferred technique is to use the Singular Value Decomposition (SVD) technique to decompose the design matrix into three separate parts: [5]

$$\begin{matrix} \{N\} = [f] \{C\} = [U] [w] [V]^T \{C\} \\ mxn \quad nxn \quad nxn \end{matrix} \quad (7)$$

The matrix  $[w]$  is a diagonal matrix with all nonnegative diagonal elements. These vectors and matrices and their various parts have interpretations from linear algebra that can be applied to the overdeterministic interfacial fracture problem. For example, since  $[w]$  is diagonal, the inverse is easily found, and linear algebra operations give the unknown coefficient vector as: [5]

$$\{C\} = [V] \cdot [diag(1/w_j)] \cdot (U^T \cdot \{N\}) \quad (8)$$

Also, the condition number of  $[f]$  can be defined as the ratio of the maximum to the minimum value of the diagonal elements of  $[w]$ . Large condition numbers indicate ill-conditioning. When the reciprocal of the condition number approaches the computational precision, the presence of ill-conditioning will significantly affect solution accuracy. If this occurs, the adverse effects can be minimized by setting the terms  $1/w_j$  in eq. (8) equal to zero for all sufficiently small  $w_j$ . In this work,  $1/w_j$  was replaced by zero if it was less than  $1 \times 10^{-12}$  of the maximum diagonal value. [5]

The effect of ill-conditioning is to produce an infinite set of solutions that all approximately solve the linear equation  $\{N\} = [f] \{C\}$ . Zeroing these diagonal elements selects from this set the solution, the one that minimizes the residual  $R = |\{N\} - [f] \{C\}|$ . The result is that the SVD method with correction is often better than both direct methods and uncorrected SVD methods, as is shown by the experimental results below. [5]

## RESULTS

Singular Value Decomposition has been used in two examples provided here. In both cases, a specimen had a heat source applied to its upper surface and a cooling plate applied to its lower surface, so that heat transfer occurred vertically and the temperature field was one-dimensional. We used implanted thermocouples to determine the temperatures and then used this data with finite element models to determine the  $J$  integral and the magnitudes of the complex stress intensity factors. Figures 1 and 2 show the two specimens. The first specimen was made from aluminum and copper, and the second was made from steel and a thermocouple cement. The material properties for the four materials are given in Table 1. The bimaterial parameters for these two combinations were 0.026 and 0.113, respectively, for the aluminum-copper and steel-cement material combinations.

Table1 Material properties for the bimaterial components

| Material            | Young's Modulus [GPa] | Poisson's ratio |
|---------------------|-----------------------|-----------------|
| aluminum            | 71.7                  | 0.34            |
| copper              | 120.0                 | 0.33            |
| steel               | 218.0                 | 0.29            |
| thermocouple cement | 3.2                   | 0.30            |

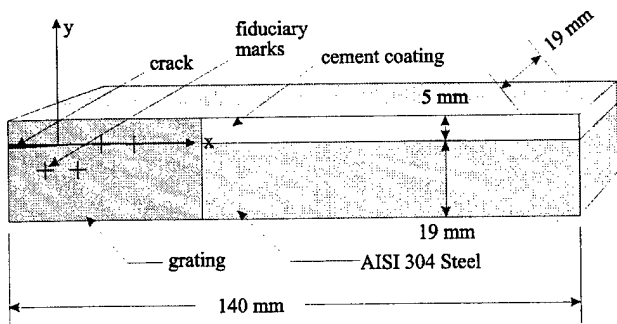


Figure 1 Geometry of the steel-thermocouple cement specimen

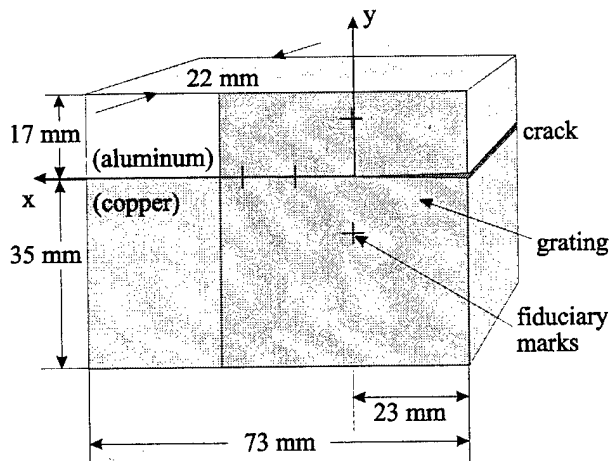


Figure 2 Geometry of aluminum-copper specimen

Identical thermal boundary conditions were applied to analogous specimens with moiré interferometry gratings. The resulting  $u_x$  displacement components were recorded as fringe patterns and used with the local collocation method. The real and imaginary parts of  $a_o$  in eq. (4) are  $a_{o_r}$  and  $a_{o_i}$  and are related to the real and imaginary parts of the complex stress intensity factor. Figure 3 shows the calculated values for  $a_{o_r}$  and  $a_{o_i}$  for the aluminum-copper specimen, and Figure 4 shows the results for the steel-cement specimen. The other curves shown in the figures are obtained using the SVD method without correcting for ill-conditioning (in test cases, the use of Gaussian elimination gave identical results to the uncorrected SVD method). Table 2 gives the magnitudes of the complex stress intensity factors calculated using the local collocation method with the SVD method and the related finite element calculations.

Table 2 Magnitude of complex stress intensity factors for the two experiments [ $\text{MPa m}^{1/2}$ ]

| Material Pair             | SVD-Local Collocation Method | Finite Element Results |
|---------------------------|------------------------------|------------------------|
| aluminum-copper           | 0.613                        | 0.601                  |
| steel-thermocouple cement | 12.1                         | 11.1                   |

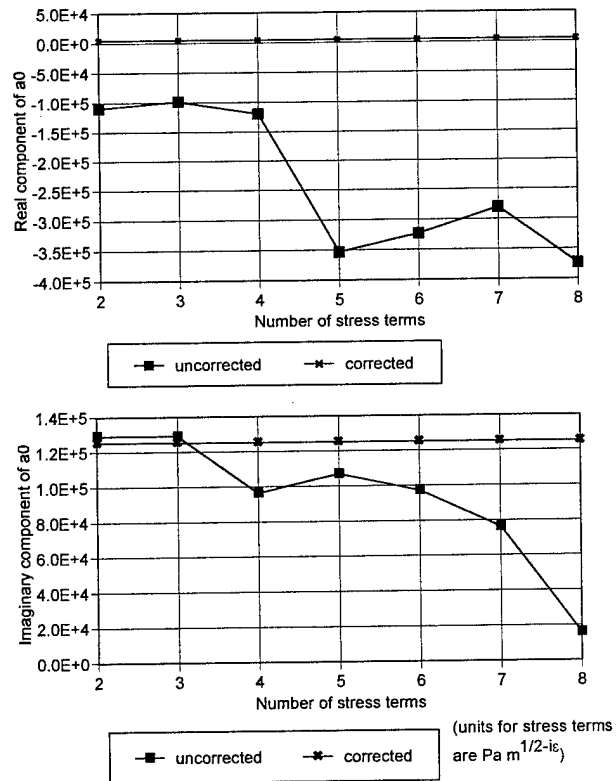


Figure 3 Comparison of results for aluminum-copper specimen

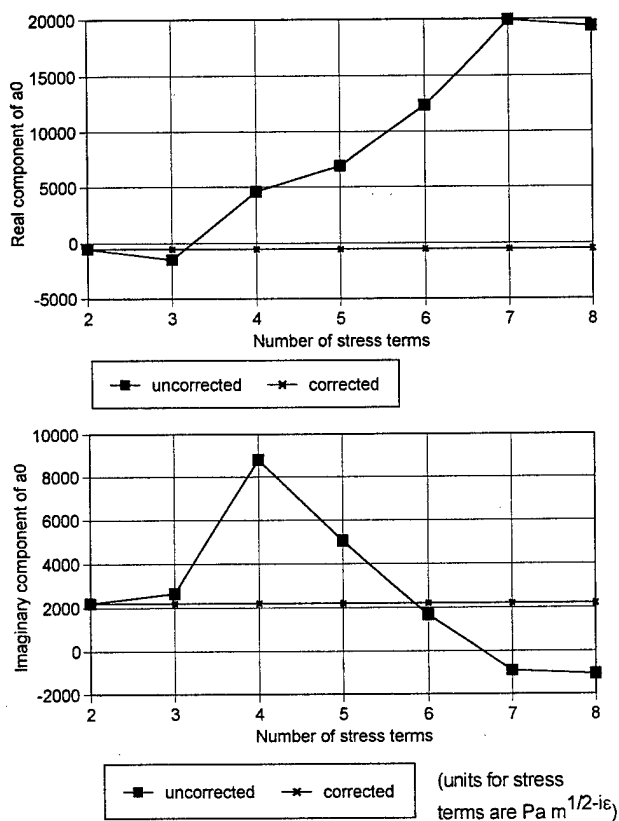


Figure 4 Comparison of results for the steel-thermocouple cement specimen

#### CONCLUSIONS

Ill-conditioning caused by a weak dependence of terms in full field interfacial crack data can cause instabilities in the solution of overdeterministic methods. An alternative solution technique, the singular value decomposition method, is available, and gives stable results that are unobtainable with direct methods. Applying this technique to experimental data for two different bimaterial combinations gave results that agreed with computational results.

#### REFERENCES

- [1] Barker, D. B., Sanford, R. J. and Chona, R., *Determining K and Related Stress-Field Parameters from Displacement Fields*, Experimental Mechanics, Vol. 25, No. 399-407, pp. 399-407, 1985.
- [2] Sanford, R. J., *Application of the Least-Squares Method to Photoelastic Specimens*, Experimental Mechanics, Vol. 20, No. 192-197, pp. 192-197, 1980.
- [3] Williams, M. L., *The Stresses around a Fault or Crack in Dissimilar Media*, Bulletin of the Seismological Society of America, Vol. 49, No. 199-204, pp. 199-204, 1959.
- [4] Miller, T. C., *An Experimental Investigation of the Fracture Mechanics of Interfacial Cracks in a Bimaterial Using the Local Collocation Method*, Ph.D.

Dissertation, Texas A&M University, College Station, Texas, 1998.

- [5] Press, W. H., Flannery, B. P. and Vetterling, W. T., *Numerical Recipes in FORTRAN: The Art of Scientific Computing*, 2nd ed., Cambridge University Press, New York, 1992.