

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB NO. 0704-0188

Public Reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comment regarding this burden estimates or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave Blank)		2. REPORT DATE March 15, 2003		3. REPORT TYPE AND DATES COVERED <del>Reprint</del>	
4. TITLE AND SUBTITLE CHEMISTRY OF OLIGONUCLEOTIDE-GOLD NANOPARTICLE CONJUGATES				5. FUNDING NUMBERS DAAG55-97-1-0133	
6. AUTHOR(S) ROBERT L. LETSINGER, CHAD A. MIRKIN, ROBERT ELOHANIAN, ROBERT C. MUCIC, and JAMES I STORHOFF					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Northwestern University Department of Chemistry Evanston IL 60208-3113				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)  U. S. Army Research Office P.O. Box 12211 Research Triangle Park, NC 27709-2211				10. SPONSORING / MONITORING AGENCY REPORT NUMBER 37257-MUR  026	
11. SUPPLEMENTARY NOTES The views, opinions and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy or decision, unless so designated by other documentation.					
12 a. DISTRIBUTION / AVAILABILITY STATEMENT  Approved for public release; distribution unlimited.				12 b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words)  Conjugates prepared by immobilizing thiol-terminated oligonucleotides onto gold nanoparticles form stable colloidal solutions in aqueous media. The oligo nucleotides can serve as linkers to organize the gold particles reversibly into three dimensional arrays, and the gold particles can function as colorimetric reporters for hybridization of the bound oligomers with target oligonucleotides in solution.					
14. SUBJECT TERMS				15. NUMBER OF PAGES 3	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OR REPORT UNCLASSIFIED		18. SECURITY CLASSIFICATION ON THIS PAGE UNCLASSIFIED		19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	
				20. LIMITATION OF ABSTRACT  UL	

NSN 7540-01-280-5500

Standard Form 298 (Rev.2-89)  
Prescribed by ANSI Std. Z39-18  
298-102

20030506 086

## CHEMISTRY OF OLIGONUCLEOTIDE-GOLD NANOPARTICLE CONJUGATES

ROBERT L. LETSINGER, CHAD A. MIRKIN, ROBERT ELGHANIAN, ROBERT C. MUCIC, and JAMES J. STORHOFF  
Department of Chemistry, Northwestern University, Evanston, IL 60208

**ABSTRACT:** Conjugates prepared by immobilizing thiol-terminated oligonucleotides onto gold nanoparticles form stable colloidal solutions in aqueous media. The oligonucleotides can serve as linkers to organize the gold particles reversibly into three dimensional arrays, and the gold particles can function as colorimetric reporters for hybridization of the bound oligomers with target oligonucleotides in solution.

**Keywords:** gold; nanoparticles; oligonucleotide; hybridization; non-radioactive detection

### INTRODUCTION

Nanoparticles coated with selected proteins have found extensive applications in immunocytochemistry<sup>[1,2]</sup>, virus diagnosis, and immunoagglutination tests<sup>[3]</sup>. Surface modified nanoparticles also show potential as building blocks in the assembly of new materials<sup>[4,5]</sup>. We summarize here the results of an exploratory study of thiololigonucleotide gold-nanoparticle conjugates. The aims were to see whether the molecular recognition features of oligonucleotides might be exploited in organizing assembly of nanoparticles, and, conversely, whether the gold nanoparticles might serve as useful reporters for hybridization of oligonucleotides.

### RESULTS


Colloidal gold solutions were prepared according to Frens<sup>6</sup> by reduction of tetrachloroauric acid with citrate. Deep red solutions exhibiting maxima at 520 nm and 260 nm were obtained. Transmission electron microscopy revealed relatively uniform spherical particles approximately 13 nm in diameter. These data in conjunction with analysis for gold by ICP showed the concentration of nanoparticles to be ~13 nM, with  $\epsilon(520) = 2.4 \times 10^8 \text{ M}^{-1}\text{cm}^{-1}$  and  $\epsilon(260) = 2.8 \times 10^8 \text{ M}^{-1}\text{cm}^{-1}$  on a particle basis.

Oligonucleotide-gold conjugates were obtained by treating the gold nanoparticles with synthetic oligonucleotides terminated at the 5'-end with HS(CH<sub>2</sub>)<sub>6</sub>OP(O)(O)- or at

the 3'-end with  $\text{HS}(\text{CH}_2)_3\text{OP}(\text{O})(\text{O})^-$ . Following aging in 0.1 M NaCl, the conjugates were collected by centrifugation, resuspended in the desired buffer-salt solution and filtered. In contrast to solutions of colloids treated with oligonucleotides lacking the thiol group, which turned blue and precipitated in solutions  $>0.2$  M in NaCl, these sols were stable even in 1 M NaCl.

The key reaction in organizing the gold conjugates and in potential diagnostic applications is hybridization, a specific association of complementary oligonucleotide strands in which adenine pairs with thymine and guanine pairs with cytosine. We have examined hybridization for a variety of gold conjugates in diverse systems. Some representative examples are provided here. Each is used to illustrate one or more features of the hybridization process; however, the features are common to all the systems. In the notation, Au represents a gold nanoparticle and s-oligonucleotide one of the many thiololigonucleotides linked to that nanoparticle.

#### Four Component System.



Although the most complex of the self assembly systems thus far investigated, this one was the first examined<sup>[8]</sup>. The target was a double stranded DNA fragment containing overhanging nucleotide sequences than could bind selectively to different nanoparticle conjugates. In 1.0 M NaCl the mixture afforded a blue solution that reverted to red on heating. The spectral shifts are depicted in Figure 1. Successive heating and cooling experiments monitored by absorbance changes at 260 nm and 700 nm further showed that the transitions are fully reversible. A plausible explanation is that hybridization of the probes with the target generates a three dimensional network of nanoparticles held in proximity by the oligonucleotide linkers. The salient features

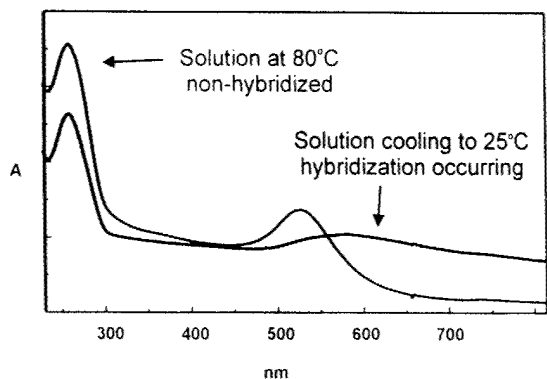


Figure 1. UV spectra for probes I + II + Target 1 at 25 °C and 80 °C.


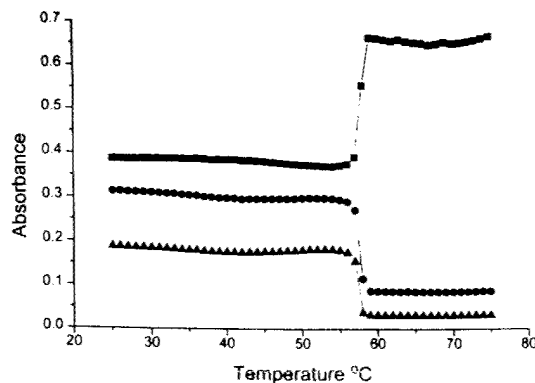


Figure 2. Dissociation curves for V+VI + Target 2 followed at 700 nm (triangles), 620 nm (circles), and 260 nm (squares).

deduced from this system are that oligonucleotides immobilized on the gold surface can hybridize with complementary oligomers in solution and that hybridization leads to an easily controlled, reversible aggregation of the nanoparticles, accompanied by shifts in both the visible and ultraviolet spectra.

#### Two Component System.




This system illustrates use of oligonucleotides in assembling nanoparticles with specified connectivity, e.g., formation of aggregates in which III is linked only to IV and IV is linked only to III. Solutions (100  $\mu\text{L}$ ) containing III and IV were either allowed to stand at 22  $^\circ\text{C}$  for a given period of time or were frozen quickly at  $-77^\circ\text{C}$  and allowed to thaw (10 min) at room temperature. Samples (3  $\mu\text{L}$ ) were then spotted on a reversed phase TLC plate and dried. The results presented in Table bring out three features. (1) The spotting technique provides a simple and rapid means for observing hybridization involving the gold conjugates; if the nanoparticles have been aggregated by hybridization of the pendant oligonucleotides, the dried spot is blue; if not, the spot is pink. (2) The rate of hybridization increases with the ionic strength of the solution (see data at 22  $^\circ\text{C}$ ). (3) The rate of hybridization can be greatly accelerated by freezing and thawing the solution. Use of the freeze-thaw cycle in conjunction with the spot tests enables one to effect and detect hybridization within a few minutes.

Table 1. Spot test for hybridization of probes III and IV

Conditions	Freeze-Thaw		Temperature = 22 $^\circ\text{C}$					
Buffer only <sup>a</sup>	<b>Blue</b>	Pink	Pink	Pink	Pink	Pink	Pink	Pink
0.1 M NaCl <sup>b</sup>	<b>Blue</b>	Pink	Pink	Pink	Pink	Pink	Mag. <sup>c</sup>	<b>Blue</b>
0.3 M NaCl <sup>b</sup>	<b>Blue</b>	Pink	Pink	Mag. <sup>c</sup>	<b>Blue</b>	<b>Blue</b>	<b>Blue</b>	<b>Blue</b>
Time (min)	10	0	10	30	60	90	300	720

(a) 10 mM phosphate. (b) In addition to the buffer. (c) Magenta.

#### Three Component System.



TARGET 2: 3'-CGCGATCTCTAGCAAAGGATAGCTGGTACGA

This combination illustrates use of the oligonucleotide-gold nanoprobe in recognizing a single stranded oligonucleotide target<sup>[9]</sup>. Dissociation of the aggregates formed by hybridization of V + VI with Target 2 (30 pmoles in 300  $\mu\text{L}$  of solution; 0.1 M NaCl; freeze-thaw procedure) was followed both by spectral changes at three different wavelengths (Figure 2) and by spot tests. In each case the observed transitions were remarkably sharp. For the spot tests the hybridized mixture was warmed in stages (increase of 0.5  $^\circ\text{C}$  for each stage, with standing at the new temperature for 5 min before spotting). The color change for the spots occurred within a 1  $^\circ\text{C}$  range; at 58.0  $^\circ\text{C}$  the

spot was blue, at 58.5 °C it was magenta, and at 59 °C it was pink<sup>[9]</sup>. We attribute the sharp breaks in the melting transition in these cases to a high degree of cooperativity in dissociating the duplex strands holding an aggregate together and to the fact that an aggregate of the conjugates can exhibit its characteristic spectrum even after dissociation of a considerable fraction of the interparticle linkages. As a consequence of the sharp melting transition, the nanoparticle probes are highly selective in recognizing oligonucleotide sequences. Probes V and VI can readily distinguish between Target II and an oligonucleotide differing by a single nucleotide<sup>[9]</sup>. For a related system we found that a 24-mer target could be identified by the spot test even in presence of four other oligonucleotides, each differing by a single nucleotide substitution, addition, or omission<sup>[10]</sup>.

In summary, oligonucleotides bound through a terminal sulfur atom to gold nanoparticles readily hybridize with other oligonucleotides free in solution or anchored to other nanoparticles. These conjugates provide a means for organizing nanoparticles into aggregates and show promise as highly selective probes for oligonucleotide targets.

#### Acknowledgments

This work was supported in part by the Cancer Center of Northwestern University and by a grant from the National Institute of General Medical Sciences (GM058356).

#### References

- [1.] S. Garzon and M. Bendayan, in *Immuno-Gold Electron Microscopy*, edited by A. D. Hyatt and B. T. Eaton, (CRC Press, Boca Raton, 1993) Chap. 6, p. 137.
- [2.] M. A. Hayat, *Colloidal Gold, Principles, Methods, and Applications, Vol.1* (Academic Press, Inc. San Diego, 1989), p.1.
- [3.] L. B. Bangs, *Pure Appl. Chem.*, **68**, 1873 (1996).
- [4.] J. J. Storhoff, R. C. Mucic, and C. A. Mirkin, *J. Cluster Science*, **8**, 179 (1997).
- [5.] C. R. Martin and D. T. Mitchell, *Anal. Chem. News & Features*, 322A (1998).
- [6.] G. Frens, *Nature Phys. Sci.* **241**, 20 (1973).
- [7.] Use of thiol groups to link organic fragments to gold surfaces is well established. See, e.g., L. H. DuBois and R. G. Nuzzo, *A. Rev. Phys. Chem.*, **43**, 437 (1992) and C.S. Weisbecker, M. V. Merritt, and G. M. Whitesides, *Langmuir*, **12**, 3763 (1996). For attachment of nucleotides through a terminal sulfur atom to gold, see R. C. Mucic, M. K. Herrlein, C. A. Mirkin, and R. L. Letsinger, *Chem. Commun.*, 555 (1996). For a report of an alternate means for attaching an oligonucleotide to a nanoparticle see A. P. Alivisatos, K. P. Johnsson, X. Peng, T. E. Wilson, C. J. Loweth, M. P. Bruchez Jr, and P. G. Schultz, *Nature*, **382**, 609 (1996).
- [8.] C. A. Mirkin, R. L. Letsinger, R. C. Mucic and J. J. Storhoff, *Nature*, **382**, 607 (1996).
- [9.] R. Elghanian, J. J. Storhoff, R. C. Mucic, R. L. Letsinger, and C. A. Mirkin, *Science*, **277**, 1078 (1997).
- [10.] J. J. Storhoff, R. Elghanian, R. C. Mucic, C. A. Mirkin, and R. L. Letsinger, *J. Am. Chem. Soc.*, **120**, 1959 (1998).