

# Aging of Dual Mode Resonator for Microcomputer Compensated Crystal Oscillator

Yoonkee Kim

U.S. Army Communications-Electronics Research, Development and Engineering Center

Fort Monmouth, NJ 07703

**Abstract**— A Microcomputer Compensated Crystal Oscillator (MCXO) utilizes the dual c-mode excitation (fundamental mode and 3<sup>rd</sup> overtone (OT)) of an SC-cut resonator for self-temperature sensing and compensation. The long-term stability of the MCXO depends primarily on the aging of the dual mode resonator. When two modes age differently in time, the aging MCXO's output frequency curve would shift with a tilt over its operating temperature range.

In this paper, we report the aging of the dual modes of the 20 MHz 3<sup>rd</sup> OT SC-cut MCXO resonators. The resonators were measured over the  $-55^{\circ}\text{C} \sim +85^{\circ}\text{C}$  temperature range with the self-temperature sensing technique utilized for the MCXO. The measured aging of the two modes ranges from 0.083 ppb to 0.386 ppb per day. The fundamental mode shows more aging than the OT. Observing the different aging of the two modes is not surprising since the mode shape effect and stress relief would be different between the two modes. The different aging rates exacerbate the long-term aging in the MCXO by increasing the offset more than the worse aging rate of the two.

## I. INTRODUCTION

A Microcomputer Compensated Crystal Oscillator (MCXO) utilizes the dual c-mode excitation (fundamental mode and 3<sup>rd</sup> overtone (OT)) of an SC-cut resonator for self-temperature sensing and compensation. The long-term stability of the MCXO depends primarily on the aging of the dual mode resonator. The presumption that the two modes may age differently in time has been of concern since the aging difference affects the long-term stability of the MCXO [1]. It was reported that the output frequency curve of an aging MCXO tilts over the operating temperature range and the aging difference between the two modes was speculated as the cause [2]. The measurement of the aging of the MCXO frequency output is found elsewhere [3], but that of the two modes, *i.e.* the primary source of the aging of the output, has not been reported yet.

Several years ago, we reported the hysteresis measurement of some 20 MHz 3<sup>rd</sup> OT SC-cut MCXO resonators, packaged in TO-5 metal cans [4]. In this paper, we present the aging of the same resonators. The aging data

were analyzed with the same self-temperature sensing technique utilized for the MCXO. A prediction of long-term aging of the resonators is also presented.

## II. MEASUREMENT METHODOLOGY

A design of a 20 MHz 3<sup>rd</sup> OT SC-cut resonator has been found to provide well-behaved characteristics for the fundamental mode and 3<sup>rd</sup> OT c-mode frequency vs. temperature for a  $-55^{\circ}\text{C}$  to  $+85^{\circ}\text{C}$  operating temperature range [4]. The resonator uses a 6.4 mm diameter blank that is plano-convex, with a 9.0 or 9.5 diopter contour. The electrodes are 3.3 mm in diameter, Cr-Au, with tabs along the X-axis. A four-point mounted crystal is packaged in an HC-35/U (TO-5).

Measuring the aging of a resonator frequency is not as straightforward as measuring an oven controlled crystal oscillator (OCXO) or a temperature compensated crystal oscillator (TCXO), whose frequency output is temperature-compensated, since, not only does the resonator frequency change with respect to temperature, but the temperature-frequency fluctuations are also greater than the aging. Rather than attempting to measure the aging at a fixed temperature, we measure it at the turning point of the frequency-temperature (F-T) curve of each mode. We utilize the self-temperature sensing of an MCXO, *i.e.* using the beat frequency rather than temperature to take advantage of its much higher resolution.

Initially, five resonators were measured in  $\pi$ -networks and three resonators were measured in dual-mode oscillators (DMXO) as shown in Fig. 1. Employing the  $\pi$ -network was to eliminate the aging associated with oscillator circuits. Simultaneous measurement of the dual modes is the key of self-temperature sensing to eliminate the temperature fluctuation error. With the  $\pi$ -network, however, it was only possible to sequentially measure the two modes, resulting in greater noise than aging. Thus, the  $\pi$ -network measurement data were discarded. The DMXO allows simultaneous measurements of the two modes by triggering the two counters simultaneously. Therefore, the data analyzed in this paper are from the DMXO measurements.

## Report Documentation Page

*Form Approved*  
*OMB No. 0704-0188*

Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

1. REPORT DATE <b>AUG 2005</b>		2. REPORT TYPE		3. DATES COVERED <b>00-00-2005 to 00-00-2005</b>	
4. TITLE AND SUBTITLE <b>Aging of Dual Mode Resonator for Microcomputer Compensated Crystal Oscillator</b>				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) <b>U.S. Army Communications-Electronics Research, Development and Engineering Ctr, Fort Monmouth, NJ, 07703</b>				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT <b>Approved for public release; distribution unlimited</b>					
13. SUPPLEMENTARY NOTES <b>Joint IEEE International Frequency Symposium and Precise Time and Time Interval (PTTI) Systems and Applications Meeting, 29-31 Aug 2005, Vancouver, BC, Canada</b>					
14. ABSTRACT <b>A Microcomputer Compensated Crystal Oscillator (MCXO) utilizes the dual c-mode excitation (fundamental mode and 3rd overtone (OT)) of an SC-cut resonator for self-temperature sensing and compensation. The long-term stability of the MCXO depends primarily on the aging of the dual mode resonator. When two modes age differently in time, the aging MCXO's output frequency curve would shift with a tilt over its operating temperature range. In this paper, we report the aging of the dual modes of the 20 MHz 3rd OT SC-cut MCXO resonators. The resonators were measured over the 75°C ~ +85°C temperature range with the self-temperature sensing technique utilized for the MCXO. The measured aging of the two modes ranges from 0.083 ppb to 0.386 ppb per day. The fundamental mode shows more aging than the OT. Observing the different aging of the two modes is not surprising since the mode shape effect and stress relief would be different between the two modes. The different aging rates exacerbate the long-term aging in the MCXO by increasing the offset more than the worse aging rate of the two.</b>					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT <b>unclassified</b>	b. ABSTRACT <b>unclassified</b>	c. THIS PAGE <b>unclassified</b>			

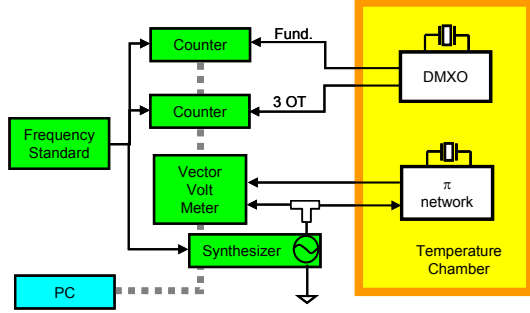


Figure 1. Measurement setup.

The measurements started at  $-55\text{ }^{\circ}\text{C}$  after a 40 minute period of stabilization. The temperature was increased to  $+85\text{ }^{\circ}\text{C}$  and then decreased back to  $-55\text{ }^{\circ}\text{C}$  in increments of  $4\text{ }^{\circ}\text{C}$ , making a temperature cycle. At each target temperature, the resonators were soaked for 30 to 50 minutes to achieve a quasi-static temperature condition. The frequencies were measured 10 times at each target temperature to obtain an average value.

Fig. 2(a) shows typical F-T curves of the fundamental mode  $f_1$  and the 3<sup>rd</sup> OT  $f_3$  and the beat frequency, defined by  $f_{\beta} = 3f_1 - f_3$ . The beat frequency shows an almost linear coefficient of  $-33.9\text{ Hz}/^{\circ}\text{C}$  and this monotonic slope in temperature is essential to make self-temperature sensing possible. Fig. 2(b) shows the mode frequencies as a function of  $f_{\beta}$  instead of temperature  $T$ . All the frequencies are referenced to the corresponding ones at the starting temperature of the cycle,  $-55\text{ }^{\circ}\text{C}$ , so that  $f_{\beta} = 0$  at  $T = -55\text{ }^{\circ}\text{C}$ . The turning points of  $f_1$  and  $f_3$  occur at  $\Delta f_{\beta} \cong -780\text{ Hz}$  ( $T \cong -27\text{ }^{\circ}\text{C}$ ) and  $\Delta f_{\beta} \cong -2170\text{ Hz}$  ( $T \cong 17\text{ }^{\circ}\text{C}$ ), respectively.

Since the frequencies were measured at discrete temperature points with  $4\text{ }^{\circ}\text{C}$  intervals, there are gaps between the frequency data. To fill the gaps, the frequency data were interpolated with curve-fittings and the maximum values are obtained for the turning points. To analyze the data, we can adopt the noise analysis found in Filler and Vig's paper [1] since the frequency changes due to aging can be regarded as noise. To describe the analysis here, some of the equations in the paper are reproduced.

Each mode frequency can be approximated with polynomials in  $f_{\beta}$

$$f_1(T) \sim F_1(f_{\beta}) = \sum C_{1j} (f_{\beta})^j \quad (1)$$

$$f_3(T) \sim F_3(f_{\beta}) = \sum C_{3j} (f_{\beta})^j \quad (2)$$

where the  $C$  represents the coefficients of the polynomials and the subscript 1 and 3 represent the fundamental mode and 3<sup>rd</sup> OT, respectively. Similarly, aging frequencies  $f_1'$  and

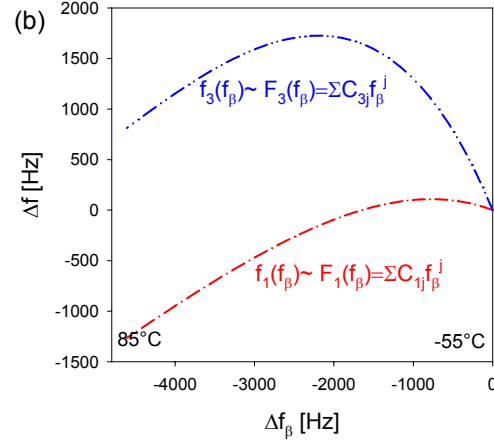
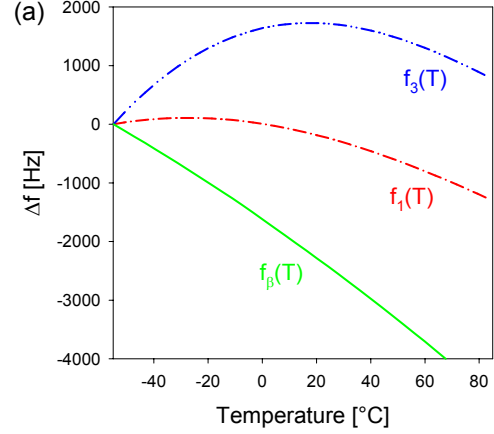


Figure 2. Fundamental and 3rd OT frequency curves as a function of (a) temperature, (b) beat frequency.

$f_3'$  perturbed by aging,  $\delta f_1$  and  $\delta f_3$ , respectively, are expressed as

$$f_1'(T) = f_1(T) + \delta f_1(T) \sim F_1'(f_{\beta}') = \sum C_{1j}' (f_{\beta}')^j \quad (3)$$

$$f_3'(T) = f_3(T) + \delta f_3(T) \sim F_3'(f_{\beta}') = \sum C_{3j}' (f_{\beta}')^j \quad (4)$$

Note that the aging data are approximated with their own polynomials with the coefficients  $C'$ , which are different from the previous  $C$ . The prime sign is used to signify the aging.

Close-up views near the turning points of the  $f_1$  and  $f_3$  of initial and aging data of a resonator are shown along with the polynomial interpolations in Figs. 3(a) and 3(b). The initial data was measured after  $\sim 3$  years had passed from the fabrication of the resonator. The aging data were measured after  $\sim 5.5$  years passed from the initial measurement. The agings at the turning points are 87 ppb and 122 ppb for  $\delta f_{10}$  and  $\delta f_{30}$ , respectively. (Because of the tilt discussed later, the  $f_{\beta}$  at the turning point of the initial  $f_1$  is not necessarily the same as the  $f_{\beta}'$  of the aging  $f_1'$ , and ditto to 3<sup>rd</sup> OT.) During the time span, the whole measurement setup was disintegrated then reassembled; thus, there could be

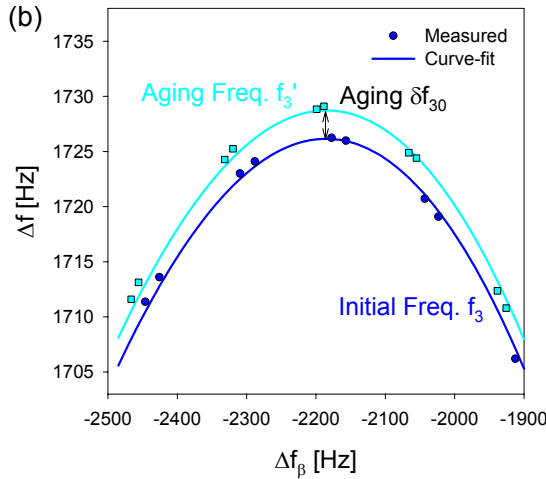
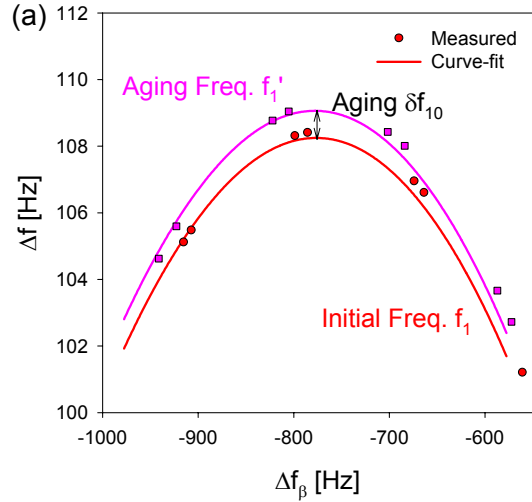


Figure 3. Aging at turning points: (a) fundamental mode, (b) 3<sup>rd</sup> OT.

measurement errors associated with this disruption. Nevertheless, the data are good enough to describe the analysis.

If the two data are plotted in a same graph in order to see the aging over the full range of  $f_\beta$ , they appear as identical curves since the difference between the two is less than a fraction of 1 % in comparison to the whole scale. To expose the minute difference, the commonly-used residuals are defined by the difference between actual data and curve fitting as follows,

$$R_1(f_\beta) = f_1(f_\beta) - F_1(f_\beta). \quad (5)$$

Applying the  $F_1$  of the initial data to the aging data instead of the  $F_1'$  reveals the aging over the full range of  $f_\beta$ , as follows

$$R_1'(f_\beta') = f_1'(f_\beta') - F_1(f_\beta'). \quad (6)$$

This operation would be analogous to an aging MCXO in which temperature is resolved by applying pre-determined polynomials to aging frequencies. (The two modes are measured with two counters here whereas a true MCXO has one counter using a mode as the time-base of the counter and the other mode as the counter input. The variation of the time-base frequency between the two methods is negligibly small [3].) The residuals of the initial and aging  $f_1$  data calculated using Eqs. (5) and (6) are shown in Fig. 4. The residual errors incidentally appear as waveforms because suboptimal polynomials were used. With better polynomials such as multi-segmented polynomials, the residual error would be minimized [1]. However, since it is intended to find the “baseline” shift due to aging rather than the optimal polynomials, non-segmented 4<sup>th</sup> order polynomials were used for simplicity. The “baseline” is the line with zero residual errors from hypothetical polynomials providing perfect curve-fitting. One can see that the baseline of the aging  $f_1$  is shifted up by  $\sim 130$  ppb with a slight tilt from that of the initial  $f_1$ . Note that the residuals of the  $f_3$  are identical with those of the  $f_1$ , as explained in [1]. Therefore, showing the residuals of the  $f_3$  is unnecessary.

Due to the tilt, obtaining the aging of each mode at the other  $f_\beta$  points than the turning points would include errors. Thus, it is assumed that the aging is uniform over temperature, so that the aging obtained at the turning point may be uniformly added (or subtracted) to the initial data across the entire temperature or  $f_\beta$  range as follows:

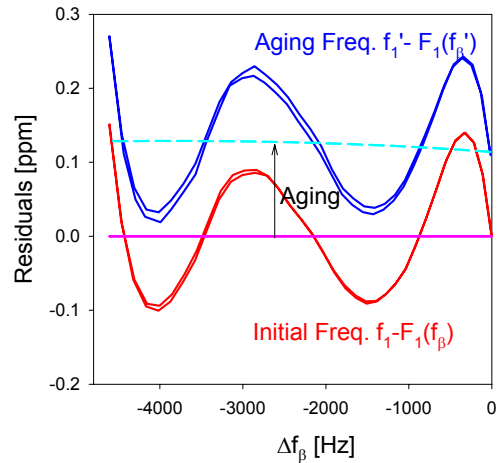


Figure 4. Frequency residuals of initial frequency and aging frequency. The baseline shifts up due to aging.

$$f'_{1a}(f_\beta) = f_1(f_\beta) + \delta f_{10} \quad (7)$$

$$f'_{3a}(f_\beta) = f_3(f_\beta) + \delta f_{30} \quad (8)$$

$$f'_{\beta a} = 3 \cdot [f_1(f_\beta) + \delta f_{10}] - [f_3(f_\beta) + \delta f_{30}]. \quad (9)$$

To substantiate the validity of this assumption, the  $f'_{\beta a}$  of the initial data shown in Fig. 4 is calculated using Eq. (9). Then, the residuals are calculated using Eq. (6) to be compared with the residuals of the measured aging  $f'_\beta$ . The results are shown in Fig. 5. The calculated residuals match very well with the measured ones, implying that the assumption is acceptable.

### III. RESULTS AND DISCUSSION

Concerning possible measurement errors in the aforementioned long-term aging data, the resonators in DMXOs were consecutively measured for about 110 days with 15 day intervals without disturbing the set-up. During the rest period between the temperature cycle measurements, the DMXOs were left at room temperature and the power supplied to the DMXOs was maintained on. The results are shown in Fig. 6. Fitting the data to linear aging curves yields the aging rates per day as shown in Table I. The OTs show lower aging rates than the fundamental modes.

Observing the different aging between the two modes is not surprising, considering the mode shapes of the two modes are different. The energy trapping in the fundamental mode spreads out more than in the OT, i.e., more tail of the energy profile in the fundamental mode falls on the quartz surface than in the OT. Two main sources of aging are due to changes of mass loading by contaminating molecules and stress relief over time [5]. Adsorption and desorption of contaminating molecules would not be the same on quartz

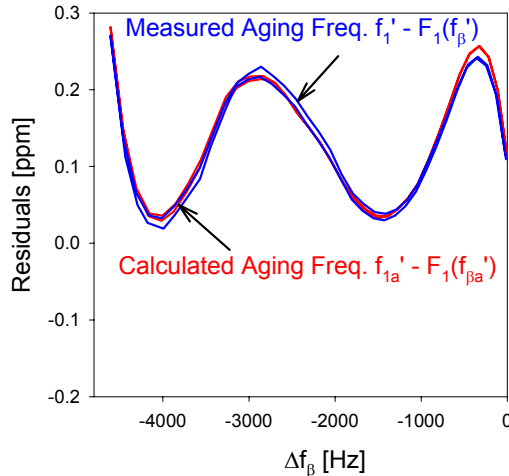


Figure 5. Comparison of the residuals of measured aging and the calculated residuals using initial data.

and gold surfaces due to the difference in the binding energy of the molecules onto the surface. Since this mass loading is weighted by the mode shapes, it would affect the fundamental mode and OT differently. It is more obvious that the stress changing over time would affect the two modes differently due to the non-uniformity in the stress distribution at the interfaces of crystal, electrodes, and mounts.

The baseline shift can be calculated using the error equation  $E(f_\beta)$  found in [1]:

$$E(f_\beta) = 3 \frac{\delta f_3}{f_3} \frac{dF_1(f_\beta)}{df_\beta} - \frac{\delta f_1}{f_1} \frac{dF_3(f_\beta)}{df_\beta}. \quad (10)$$

Assuming the linear aging rates remain the same, the long-term predictions for the baseline shifts of the three resonators are shown in Fig. 7. After 15 years, the resonator No. 1 would change by 0.63 ppm and 0.45 ppm for  $f_1$  and  $f_3$ , respectively, and because of the tilt, the baseline would have the maximum offset of 0.8 ppm at  $-55^\circ\text{C}$ . The resonator No. 3 would change by 2.11 ppm and 0.59 ppm for  $f_1$  and  $f_3$ , respectively, and the baseline would have the maximum offset of 3.5 ppm at  $-55^\circ\text{C}$ . The tilt caused by the different aging rates inflicts more offset in the baseline than the worse aging rate. Furthermore, the more difference causes the more offset.

If both  $f_1$  and  $f_3$  have the same aging rate as  $\delta f_1/f_1$ , the baseline would shift by  $\delta f_1/f_1$  without tilt (i.e. a constant in terms of  $f_\beta$ ) as evidenced by,

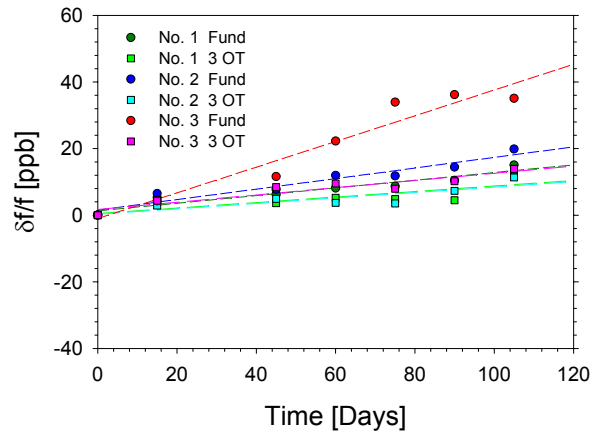


Figure 6. Measured aging rates and linear curve-fits.

TABLE I. AGING RATES PER DAY OF DUAL MODES AND THE RATIOS.

Resonator	$\delta f_1$	$\delta f_3$	$\delta f_1/\delta f_3$
No. 1	0.115 ppb	0.083 ppb	1.4
No. 2	0.158 ppb	0.082 ppb	1.9
No. 3	0.386 ppb	0.108 ppb	3.6

$$E(f_\beta) = \left( 3 \frac{dF_1(f_\beta)}{df_\beta} - \frac{dF_3(f_\beta)}{df_\beta} \right) \frac{\delta f_1}{f_1} = \frac{\delta f_1}{f_1} \quad (11)$$

since

$$3 \frac{dF_1(f_\beta)}{df_\beta} - \frac{dF_3(f_\beta)}{df_\beta} = 1 \quad (12)$$

as shown in [1]. However, as discussed above, the aging rates are expected to be different. The efforts for reducing the aging offset in an MCXO resonator aim for producing a dual mode resonator with low aging for the both modes.

#### IV. CONCLUSION

The aging rate of the fundamental mode of a dual mode SC-cut resonator for an MCXO is not the same as that of the 3<sup>rd</sup> OT. The aging rates are different between the two modes because the mode shape effects on mass loading of the contaminating molecules and stress relief are affecting the two modes differently. The different aging rates cause an offset with a tilt in the MCXO frequency output over the operating temperature range. The tilt exacerbates the long-term aging in the MCXO by inflicting more offset than the worse aging rate.

#### REFERENCES

- [1] R. L. Filler and J. R. Vig, "Resonators for the microcomputer compensated crystal oscillator," *43rd Ann. Symp. Freq. Contr.*, pp. 8-15, 1989.
- [2] E. Jackson, "The microcomputer compensated crystal oscillator – practical application of dual-harmonic mode quartz thermometry," *Proc. IEEE Int. Ultrason. Ferroelec. Freq. Contr. Conf.*, pp. 401-405, 2004.
- [3] R. L. Filler, J. A. Messina, and V. J. Rosati, "Frequency-temperature and aging performance of microcomputer compensated crystal oscillators," *43rd Ann. Symp. Freq. Contr.*, pp. 27-33, 1989.
- [4] Y. Kim, B. Rose, T. Schuyler, and J. R. Vig, "Hysteresis measurement of 20 MHz third overtone SC-cut MCXO resonators," *Proc. IEEE Int'l Freq. Contr. Symp.*, pp.126-129, 1998.
- [5] J. R. Vig and T. R. Meeker, "The aging of bulk acoustic wave resonators, filters and oscillators," *45th Ann. Symp. Freq. Contr.*, pp. 77-101, 1991.

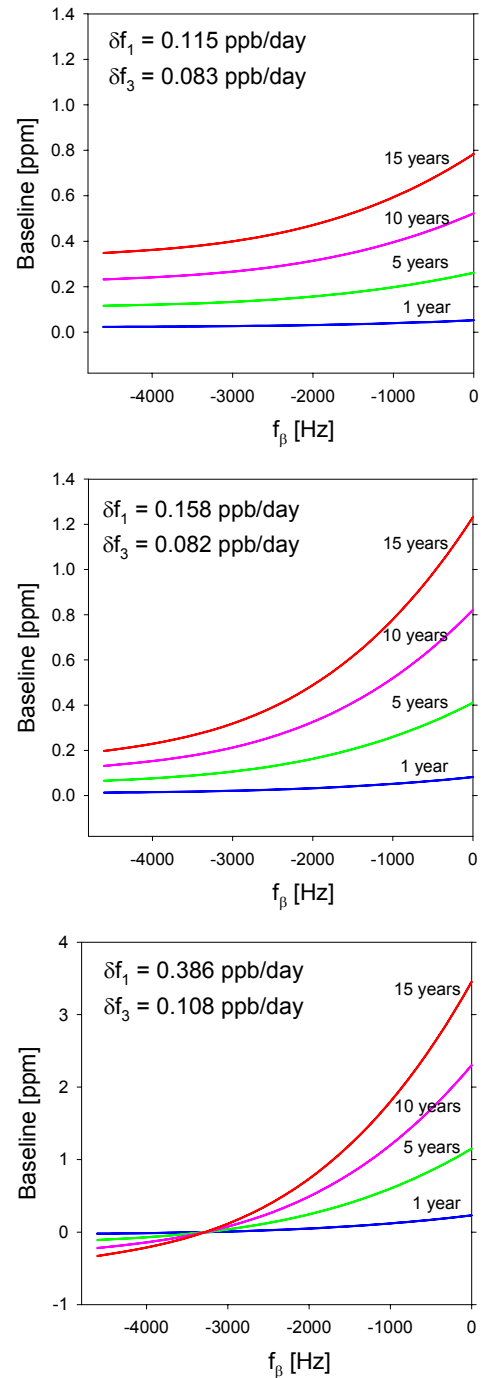


Figure 7. Predicted long-term aging of the baseline shifts for the measured aging rates shown in Table I.