

UNCLASSIFIED

AD NUMBER

ADA492300

CLASSIFICATION CHANGES

TO: UNCLASSIFIED

FROM: CONFIDENTIAL

LIMITATION CHANGES

TO:  
Approved for public release; distribution is unlimited.

FROM:  
Distribution authorized to DoD only; Foreign Government Information; DEC 1954. Other requests shall be referred to British Embassy, 3100 Massachusetts Avenue, NW, Washington, DC 20008.

AUTHORITY

DSTL ltr dtd 16 Feb 2007; DSTL ltr dtd 16 Feb 2007

THIS PAGE IS UNCLASSIFIED

47/54

204967

COPY No. 37

~~CONFIDENTIAL~~  
~~MHA~~



MINISTRY OF SUPPLY

1. THIS INFORMATION IS DISCLOSED ONLY FOR OFFICIAL USE BY THE RECIPIENT GOVERNMENT AND SUCH OF ITS CONTRACTORS, UNDER SEAL OF 'SECURITY', AS MAY BE ENGAGED ON A DEFENCE PROJECT. DISCLOSURE TO ANY OTHER GOVERNMENT OR RELEASE TO THE PRESS OR IN ANY OTHER WAY WOULD BE A BREACH OF THESE CONDITIONS.
2. THE INFORMATION SHOULD BE SAFEGUARDED UNDER RULES DESIGNED TO GIVE THE SAME STANDARD OF SECURITY AS THAT MAINTAINED BY HER MAJESTY'S GOVERNMENT IN THE UNITED KINGDOM.
3. THE RECIPIENT IS WARNED THAT INFORMATION CONTAINED IN THIS DOCUMENT MAY BE SUBJECT TO PRIVATELY OWNED RIGHTS.

# ARMAMENT RESEARCH ESTABLISHMENT

REGRADED *U.K. Restricted* BY AUTHORITY OF *PARDE* *Reclass List No. 36*  
 DATED *8/20/70* BY *Long*

## REPORT 47/54

WICATINNY ARSENAL  
TECHNICAL INFORMATION SECTION

### WEAPONS RESEARCH DIVISION

**20081208288**

### Controlled Fragmentation XXXV. A Technique for the Study of the Cutting Action of Grooved Charges on Steel

T. W. Taylor

Safety in Mines Research Establishment, Buxton

REGRADED ~~*Confidential-MHA*~~ BY AUTHORITY OF ~~*PARDE*~~

DATED ~~*31 Mar '66*~~ BY ~~*M. Williams*~~

*1642*

*37*  
*Dec #1*  
*oc/ma/3-270*  
*11/11*  
*18574*  
*MHA*

Fort Halstead,  
Kent.

*Reg m 6763*

~~CONFIDENTIAL~~  
~~MHA~~

December  
1954

This Document was graded  
**CONFIDENTIAL**  
at the 71st meeting of the A.R.E.  
Security Classification Committee.

**THIS DOCUMENT IS THE PROPERTY OF H.B.M. GOVERNMENT  
AND ATTENTION IS CALLED TO THE PENALTIES ATTACHING  
TO ANY INFRINGEMENT OF THE OFFICIAL SECRETS ACTS**

It is intended for the use of the recipient only, and for communication to such officers under him as may require to be acquainted with its contents in the course of their duties. The officers exercising this power of communication are responsible that such information is imparted with due caution and reserve. Any person other than the authorised holder, upon obtaining possession of this document, by finding or otherwise, should forward it together with his name and address in a closed envelope to:-

**THE SECRETARY, MINISTRY OF SUPPLY, ADELPHI, LONDON, W.C. 2**

Letter postage need not be prepaid, other postage will be refunded. All persons are hereby warned that the unauthorised retention or destruction of this document is an offence against the Official Secrets Acts.

A.R.E.  
Publishing Section

MINISTRY OF SUPPLY

Extra-mural research contract

with

SAFETY IN MINES RESEARCH ESTABLISHMENT, BUXTON

A.R.E. REPORT 47/54

Controlled Fragmentation XXXV. A technique for the study of the cutting action of grooved charges on steel

by

T.W. Taylor, B.Sc.

CONTENTS

	Page
SUMMARY	1
1. INTRODUCTION	1
2. EXPERIMENTAL	1
2.1 Steel targets	1
2.2 Former for preparation of charges	1
2.3 Charge and initiation	2
2.4 Reproduction of the cut	2
2.5 Measurement of the cut	2
3. DISCUSSION	2
4. APPENDIX	4-9

Approved

..... H. Tiltman ..... for Director, S.M.R.E.

..... W. Blackman ..... Senior Superintendent, A.R.E.

~~SECRET~~  
**IMPORTANT**

This DOCUMENT should be returned to the Chief Information Officer Armament Research Establishment, Fort Halstead, Sevenoaks, Kent, if retention becomes no longer necessary.

INITIAL DISTRIBUTION

Internal

No. 1 CSAR  
2 SEMP  
3 SEMP - Att. Mr. T.W. Taylor  
4 - Mr. G.T. Laing (Shoeburyness)  
5 RO & Ed

United Kingdom

6-7 CS/ERDE  
8 DWR(D)  
9-18 Director, SMRE  
19 AWRE - DD  
20-21 - SFR  
22 CEAD  
23 DGFV  
24 DRAE (GW)  
25-26 MC of S  
27-28 Royal School of Tank Technology  
29-30 Sec. A.A. Lethality Committee (OB)  
31 Sec. OB  
32 - Att. Mr. Bishop  
33 Prof. Pearson, University College, London

Overseas (through TPA3/TIB)

34-51 US - Joint Reading Panel  
52 - Assist Sec. of Def. for Res. and Dev.  
53 - Applied Physics Laboratory, Johns Hopkins  
University (Att. Dr. C.F. Meyer)  
54 - Ballistics Res. Lab. Aberdeen  
(Att. Dr. T.E. Sterne)  
55 - Naval Ordnance Lab. Exp. Div.  
(Att. Dr. Paul Fye)  
56-57 BJSM - P.O. Box 680, Benjamin Franklin Station,  
Washington, D.C. (Att. Mr. J.W. Gibson,  
Dr. C.G. Lawson)  
58 Canada - Dept. Nat. Def.  
59-62 - Def. Res. Liaison  
63 - Nat. Res. Council  
64-65 TPA3/TIB - Retention

Stock

66-81

~~SECRET~~  
**AHM**

SUMMARY

Cylindrical charges with a longitudinal groove along one side were detonated in contact with a smooth steel block. A simple technique for measuring the depth of cut and deformation of the steel has been devised. It was possible to correlate the dimensions of the groove with the depth of cut obtained and the technique provides a simple means of comparing the efficiency of different shapes of groove.

1. INTRODUCTION

During the development of the grooved-charge method of controlling fragmentation the comparison of the effectiveness of groove profiles was carried out by comparing the fragmentation produced when the different profiles were used in similar charges in identical casings. Only experiments with V-shaped grooves have been reported.

This method is laborious and slow and is only indirect: numerical evaluation is not possible and extrapolation of the results to other circumstances is difficult. Moreover, comparison is only possible where the expected control is close to optimum for the casing.

In thick-walled casings it is not always possible to obtain the desired fragment size with V-shaped grooves since the base of the groove for optimum apex angle and depth becomes too large. It is possible that there is a more efficient shape of groove on a narrower base, and if this could be used the limiting fragment size for a given wall thickness would be reduced.

A simple and rapid technique for comparing the cutting action of different grooves was therefore desired. Such a method has now been devised and tested by comparing the cuts produced in steel blocks by various V-shaped grooves in a standard charge of H.E.

2. EXPERIMENTAL

2.1 Steel targets - The steel blocks used as targets consisted of short lengths cut from a round mild steel bar,  $3\frac{3}{4}$ -in. diameter with the ends smooth finished by surface grinding. Two thicknesses of block were used, viz., 3-in. for experiments E1, E2, E3 and D1 and 2-in. for the remainder. The blocks 2-in. thick were not split by the charges more than the 3-in. thick blocks and the measurements taken on both sizes did not differ significantly.

The blocks were thrown a considerable distance by the detonation of the charge but were not damaged appreciably.

2.2 Former for preparation of charges - To prepare the charges with a groove down one side a special cylindrical brass mould was made (Fig. 1). The mould was 3 in. long and 1 in. internal diameter and was divided longitudinally into two halves so that the cast charges could be more easily removed. A slot was milled in the wall part way along one section of the mould and a series of five interchangeable brass groove profiles were made which could be fitted into this slot as required. The details of the profiles used are shown in Table 1.

With the particular brass groove profiles used for these experiments the fit between the base of the profile and the inner wall of the mould was not always perfect. During casting of the charge a little explosive sometimes flowed between the two and when the charges were withdrawn this lip was broken and caused some chipping of the corner formed by the base of the groove and surface of the charge. Although the amount of chipping did not appear to affect the results obtained in these experiments it is clearly desirable to arrange as good a fit as possible between the groove profile and inner face of the mould.

2.3 Charge and initiation - The mould was greased slightly with vaseline and placed upright on a smooth glass plate: a cellophane filler-cap was fitted to the top. The charge was then cast in the normal way from 'cloudy' CE/TNT 30/70. Perfect charges were not easy to obtain and care was necessary when extracting the charges from the mould to avoid damage. Details of the weights of charges and condition of the groove corners are given in Table 2.

Detonation of the charge was obtained by means of a tetryl booster 1-in. diameter and 0.25-in. thick held in position at one end of the cylinder by means of a 1-in. diameter wooden plug and cellophane tape. The wooden plug was drilled centrally to take a No. 6 commercial detonator and thus hold it in position with the end in contact with the tetryl booster. A view of the complete charge in position on a target is shown in Fig. 2.

2.4 Reproduction of the cut - Direct measurement of the depth of cut in the block is not easy as it is necessary to section the block at many points across the cut or to obtain an accurately lined-up section along the length of the cut. It was therefore decided to obtain a reproduction, in relief, of the damage by casting a disk of Wood's metal on to the surface.

A length of cellophane was wrapped tightly round the periphery of the target and extended a little more than  $\frac{1}{4}$  in. above the damaged surface. The target was then warmed on a hot-plate and molten Wood's metal poured over the damaged area to give a depth of about  $\frac{1}{4}$  in. It is necessary to avoid over-heating of both target and Wood's metal as this causes blow-holes in the casting. Just before the Wood's metal sets two bolts were inserted to provide threaded holes which could be used for later removal of the casting.

When the metal had cooled, the excess cellophane standing proud of the Wood's metal was cut away, the bolts were withdrawn and the casting, still in position on the target, was faced up in a lathe. This ensured that the finished surface was as nearly as practicable parallel to the original surface of the target. The cellophane was then removed entirely and by replacing the two bolts the target and Wood's metal disk could be carefully separated.

With suitable care in casting it was found possible to obtain a good relief copy of the cut in the steel and measurements could be easily made using a micrometer and surface plate. A photograph of a typical disk is shown in Fig. 3.

2.5 Measurement of the cut - The flat face of the Wood's metal was placed on a surface plate and the height of various points in the relief were measured by means of a micrometer. There were two areas at the extreme edges of the block on either side of the cut which were not affected by the explosion. These areas on the relief therefore served as a reference level and the height of the relief above this indicated the depth of cut in the steel.

The position of the junction between the tetryl booster and main charge could be clearly seen on the relief. With this point as zero the height of the relief was measured at  $\frac{1}{4}$ -in. intervals along the ridge: the micrometer head was  $\frac{1}{4}$ -in. in diameter and hence the maximum depth of cut within each  $\frac{1}{4}$ -in. interval was obtained. The measurements for different profiles are given in Tables 3 to 6 and the results are summarized in Table 7.

Measurements were also taken of the deformation of the surface at the side of the cut and the width of the cut and from the composite measurements a section of the deformed surface can be built up. This is illustrated in Fig. 4 which shows the relevant measurements used to compare the efficiencies of different groove profiles.

### 3. DISCUSSION

From targets E1 and D1 repeat Wood's metal castings were made and measured. The measurements are included in Tables 3 to 5 and it appears that the variation between repeat castings is less than the variation

between repeat experiments. It is also clear from these results that the thickness of casting is not critical.

If the mechanism of cutting is considered, it seems likely that the cut  $d_2$  is first produced in the block by the Mumroe jet and at a slightly later stage there is the general deformation  $d_1$  due to the proximity of the body of the charge. When different profiles are to be compared, therefore, chance variation between the strengths of different targets can be eliminated if the ratio  $d_2/d_1$ , which may be called the relative depth of cut, is considered and not the absolute depth of cut. The variation of this ratio with groove depth for the two angles used has been plotted in Fig. 5 and it appears that, for each angle, the relative depth of cut is directly proportional to the depth of groove in the charge. The proportionality differs for the two angles.

If grooves of different angles but equal widths of base are compared (experiments E, A and B, C in Table 7) it is seen that equal depths of cut were obtained.



4. APPENDIX

Table 1 - Dimensions of groove formers

Groove letter	Depth of groove, in.	Base of groove, in.	Apex angle of groove
E	0.226	0.257	59°12'
A	0.176	0.258	72°30'
B	0.171	0.194	59° 6'
C	0.133	0.196	72°54'
D	0.124	0.145	60°36'

Table 2 - Details of charges

Groove letter and expt. no.	Charge weight gram	Quality of edges of grooves
A1	59.8	Fair
A2	59.4	Good
A3	60.0	Rather poor
B1	60.2	Fair
B2	59.4	Good
B3	60.0	Good
C1		Fair
C2	61.0	Fair
C3	60.5	Fair
D1		
D2	60.9	Good
D3	60.8	Good

Table 3 - Measurements of relief (D): peak height of ridge above reference level, mils

Position along ridge, in.	Groove letter and experiment number																		Repeat castings	
	E			A			B			C			D			E	D			
	1	2	3	1	2	3	1	2	3	1	2	3	1	2	3	1	1			
0.25	117	107	113	133	110	108	103	107	114	101	105	100	93	91	102	107	87			
0.50	109	105	97	118	106	103	90	84	100	95	107	97	93	90	99	104	86			
0.75	117	119	107	113	109	102	91	85	98	92	103	91	89	91	94	114	84			
1.00	119	122	112	119	104	100	91	95	94	96	111	93	90	92	93	121	83			
1.25	129	118	112	121	104	111	99	102	101	92	108	94	92	97	95	124	86			
1.50	130	117	113	111	107	110	103	100	106	106	102	95	95	92	95	128	90			
1.75	122	126	117	109	110	111	102	94	115	101	106	106	95	90	94	120	99			
2.00	128	117	115	107	107	117	99	102	105	102	101	106	98	93	92	126	98			
2.25	132	118	122	105	101	120	105	97	103	108	114	99	99	99	98	128	93			
2.50	134	121	128	114	116	134	107	98	95	112	113	103	98	98	86	130	96			
2.75	140	121	129	113	110	132	112	96	94	93	103	103	97	95	85	134	90			
Thickness of disk at two sides	182	339	281	206	246	269	224	243	296	238	218	236	279	346	290	196	249			
	184	340	283	205	251	270	212	249	295	236	217	235	341	280	198	198	249			
Mean	125	117	115	115	108	113	100	96	102	100	107	99	94	93	94	121	90			
Mean for each groove	119			112			99			102			94							
S.D. for each groove	9.1			8.6			7.3			5.9			3.9							

Table 4 - Measurement of relief ( $d_1$ ): height of rim above reference level, mils

Position along ridge, in.	Groove letter and experiment number															Repeat castings	
	E			A			B			C			D			E	D
	1	2	3	1	2	3	1	2	3	1	2	3	1	2	3	1	1
0.25	33	31	29	47	29	26	35	30	43	35	41	36	37	45	48	23	36
0.50	37	32	32	47	31	30	37	33	44	37	42	37	48	48	28	39	39
0.75	38	33	33	45	33	31	37	33	42	40	42	40	43	47	30	41	41
1.00	38	37	34	42	34	36	39	36	41	39	42	41	44	46	31	42	42
1.25	38	37	37	39	36	36	39	38	39	40	42	41	45	45	31	42	42
1.50	39	39	41	38	37	38	40	39	38	40	43	39	46	45	32	45	45
1.75	42	42	44	37	37	42	42	43	38	41	43	40	47	45	36	45	45
2.00	46	43	47	34	40	51	43	45	38	42	44	40	48	45	39	46	46
2.25	49	46	48	34	43	48	50	48	39	43	46	41	49	48	41	47	47
2.50	56	49	53	33	43	53	51	50	41	44	48	43	50	49	46	49	49
2.75	59	53	60	30	45	54	50	49	38	44	49	42	49	49	48	48	48
Mean	43	40	42	39	37	40	42	40	40	40	44	40	46	47	44	35	44

Table 5 - Measurement of relief (d<sub>2</sub>): peak height of ridge above rim, mils

Position along ridge, in.	Groove letter and experiment number												Repeat castings				
	E			A			B			C			D			E	D
	1	2	3	1	2	3	1	2	3	1	2	3	1	2	3	1	1
0.25	83	77	86	85	84	83	67	79	71	64	65	63	56	51	52	83	51
0.50	73	75	69	71	77	74	52	53	56	56	56	60	50	41	44	75	47
0.75	79	87	78	68	78	73	54	53	56	50	62	49	45	43	45	82	43
1.00	81	87	80	76	74	65	48	61	53	56	70	52	46	45	46	92	42
1.25	92	80	78	82	70	76	59	66	64	50	67	52	51	52	48	93	45
1.50	92	81	74	72	72	73	62	62	68	65	61	56	48	46	50	95	46
1.75	81	84	75	72	75	70	60	54	76	60	64	66	51	44	50	84	46
2.00	82	75	71	72	67	67	54	58	67	60	58	66	50	47	49	83	53
2.25	84	73	77	70	61	73	54	51	65	65	69	58	50	49	53	89	48
2.50	82	73	73	80	76	81	55	50	55	68	61	60	48	48	42	86	48
2.75	84	70	68	82	68	79	61	49	57	57	56	61	48	44	44	86	45
Mean	83	78	75	75	73	74	57	58	63	59	63	59	49	46	48	86	47
Mean for groove	79			74			59			60			48				
S.D. of Mean	6.2			5.8			7.6			5.7			3.5				

Table 6 - Measurement of widths: maximum width of ridge, mils

Position along ridge, in.	Groove letter and experiment number														
	E			A			B			C			D		
	1	2	3	1	2	3	1	2	3	1	2	3	1	2	3
0	138	126	130	122	114	110	106	118	110	110	94	134	63	83	87
0.50	102	118	110	114	110	106	102	110	94	90	90	78	75	75	75
1.00	142	126	122	114	102	94	114	98	90	87	94	78	90	87	79
1.50	122	114	130	102	90	118	110	106	118	83	83	90	98	67	90
2.00	110	138	122	98	90	106	83	90	110	83	79	78	83	79	75
2.50	106	106	122	138	90	118	90	98	90	94	98	78	67	75	71
Mean	120	121	123	115	99	109	101	103	102	89	90	87	79	78	79
Mean for groove	121			108			102			89			79		

Table 7 - Summary of results

Groove letter	Mean height d <sub>1</sub> mils	Mean height d <sub>2</sub> mils	Relative depth of cut d <sub>2</sub> /d <sub>1</sub>	Mean width of relief mils
E	42	79	1.88	121
A	39	74	1.89	108
B	41	59	1.43	102
C	41	60	1.46	89
D	46	48	1.04	79

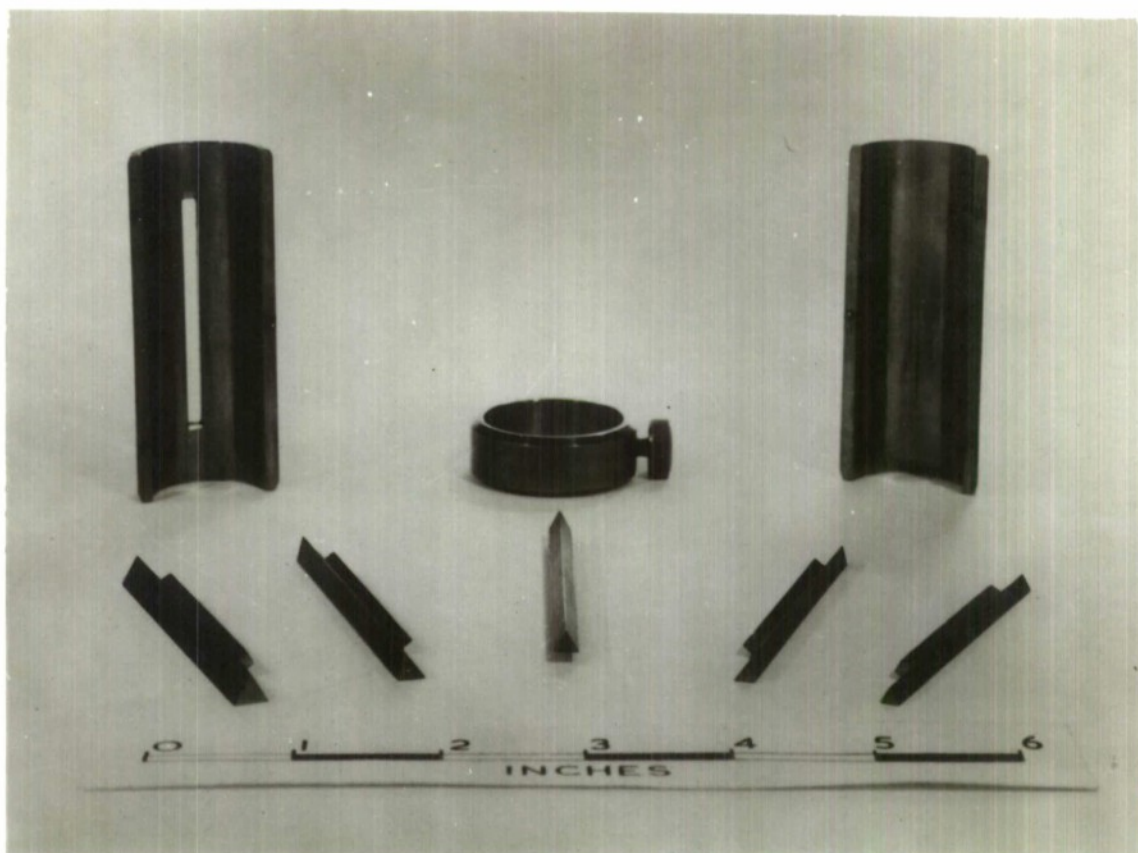


FIG.1

Brass mould and groove formers


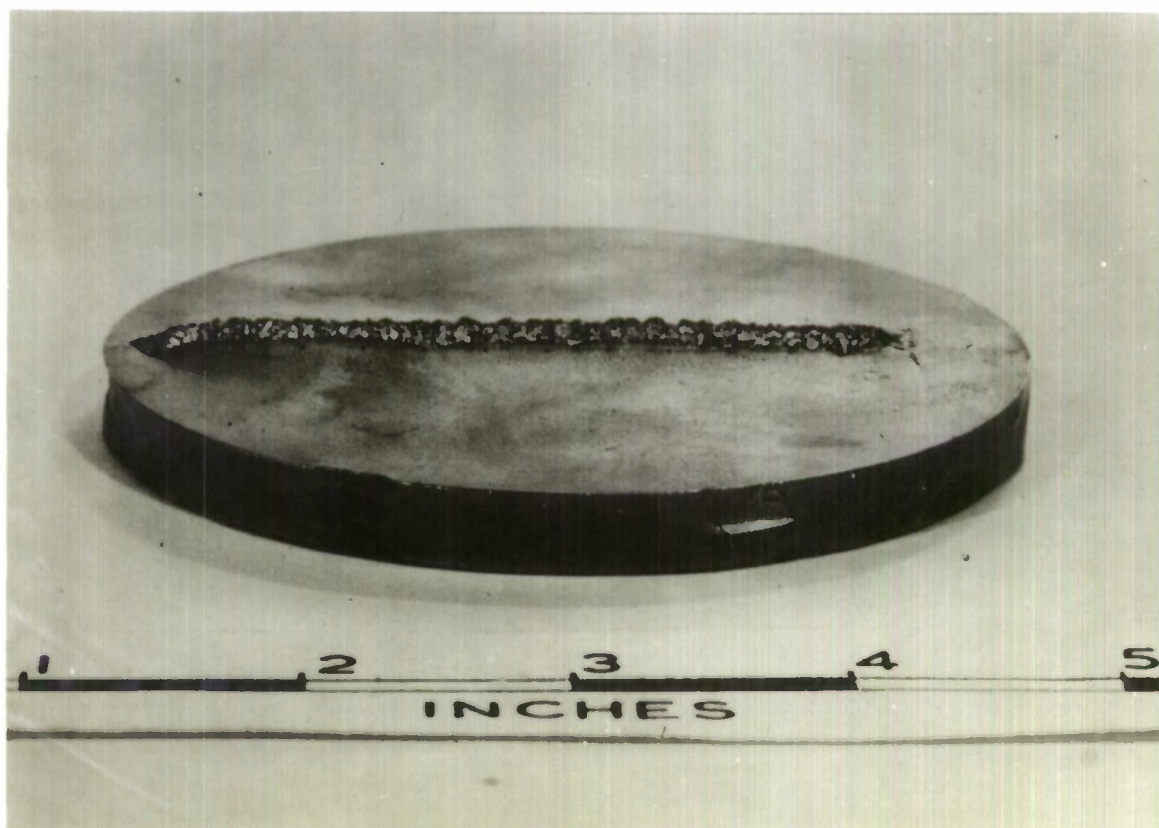


FIG.3


View of cast Wood's metal disk

~~CONFIDENTIAL~~

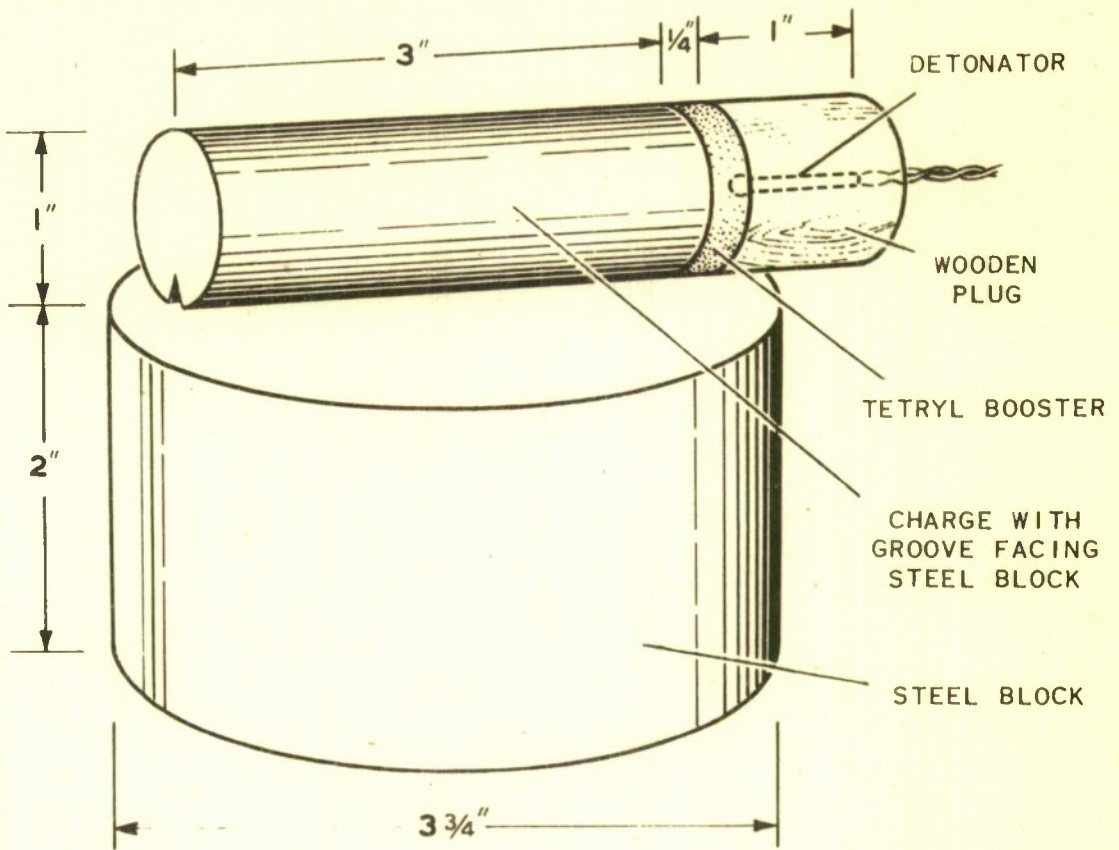

CHARGE IMMEDIATELY BEFORE DETONATION

FIG. 2

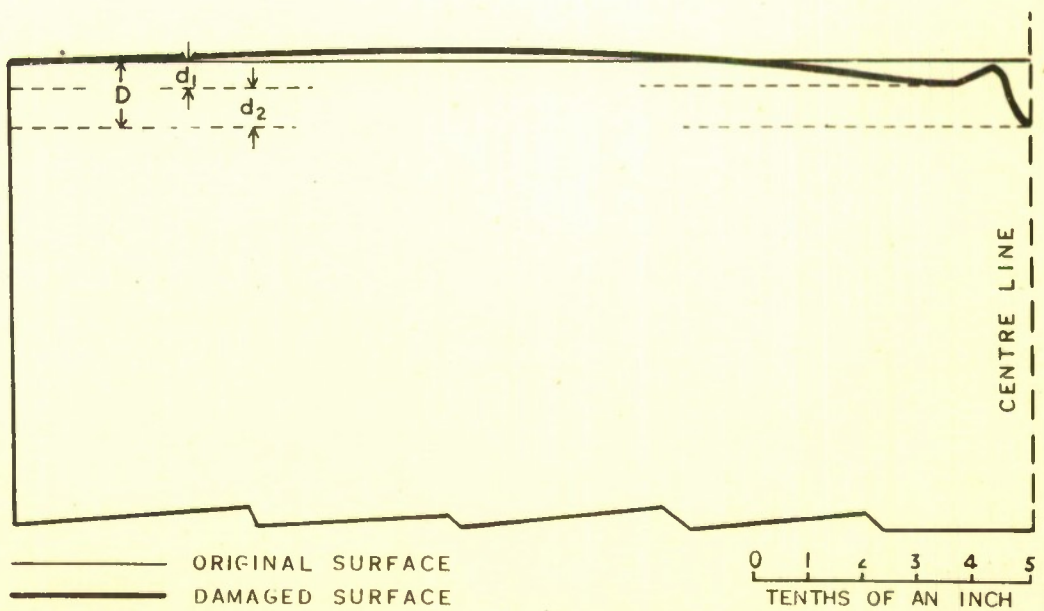


SECTION OF HALF OF DAMAGED TARGET

FIG. 4



~~CONFIDENTIAL~~

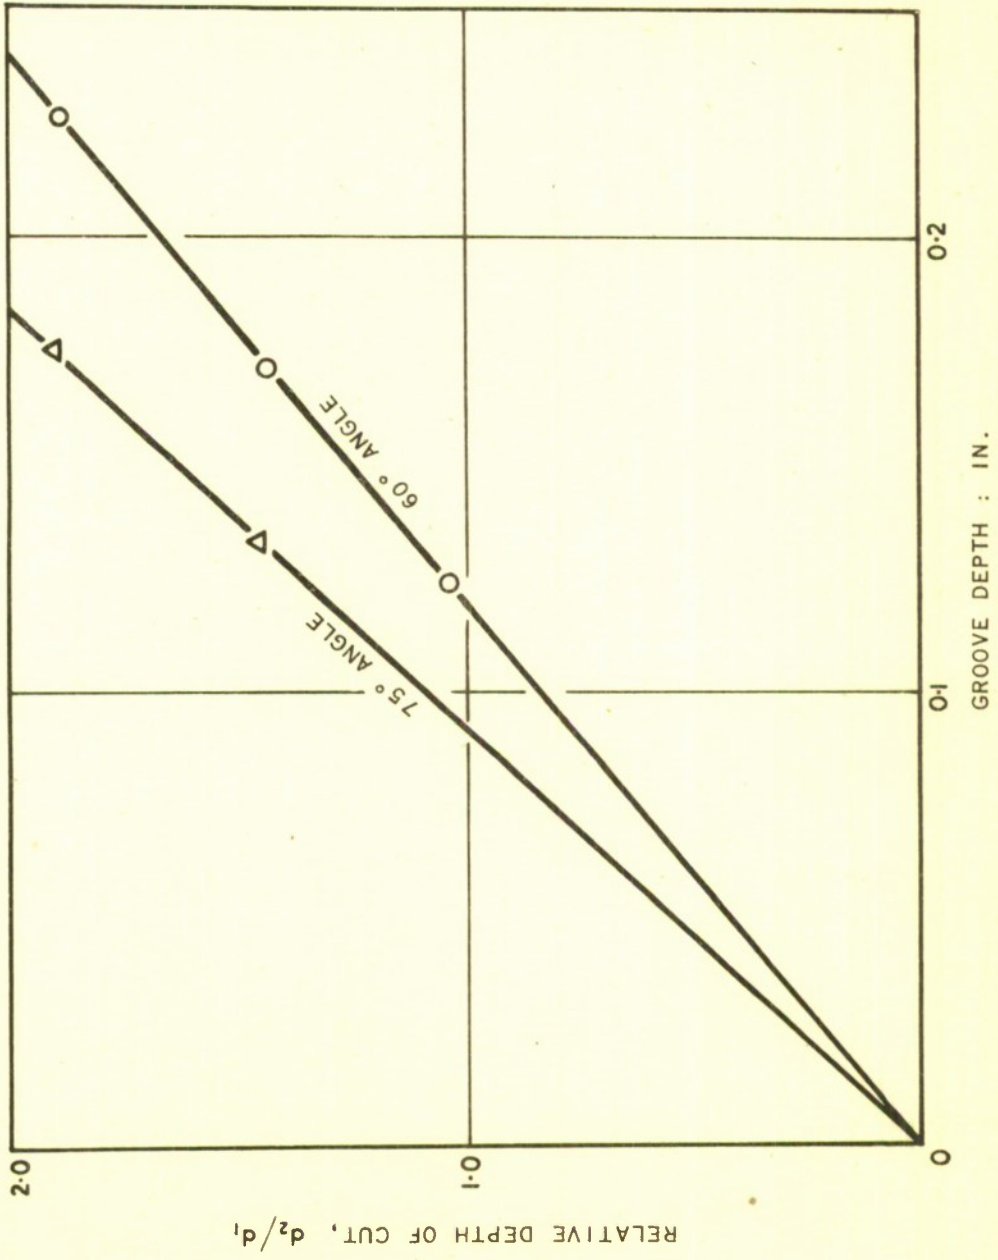

RELATION BETWEEN RELATIVE DEPTH OF CUT AND GROOVE DEPTH  
FIG. 5



*Information Centre  
Knowledge Services*  
**[dstl]** Porton Down,  
Salisbury  
Wiltshire  
SP4 0JQ  
Tel: 01980-613753  
Fax 01980-613970

Defense Technical Information Center (DTIC)  
8725 John J. Kingman Road, Suit 0944  
Fort Belvoir, VA 22060-6218  
U.S.A.

AD#:  
Date of Search: 16 February 2007

Record Summary:

Title: Controlled fragmentation, XXXV: a technique for the study of the cutting action of grooved charges on steel  
Covering dates 1954 Dec 01 - 1954 Dec 31  
Availability Open Document, Open Description, Normal Closure before FOI Act: 30 years  
Former reference (Department) ARE Report 47/54  
Note With drawings and photographs  
Held by The National Archives, Kew

This document is now available at the National Archives, Kew, Surrey, United Kingdom.

DTIC has checked the National Archives Catalogue website (<http://www.nationalarchives.gov.uk>) and found the document is available and releasable to the public.

Access to UK public records is governed by statute, namely the Public Records Act, 1958, and the Public Records Act, 1967.  
The document has been released under the 30 year rule.  
(The vast majority of records selected for permanent preservation are made available to the public when they are 30 years old. This is commonly referred to as the 30 year rule and was established by the Public Records Act of 1967).

**This document may be treated as UNLIMITED.**