

Underwater Adhesives/Attachments

Billy Courson
Naval Surface Warfare Center
Coastal Systems Station-Dahlgren Division
Panama City, FL 32408
phone: (850) 235-5708 fax: (850) 235-5879 e-mail: CoursonBF@ncsc.navy.mil
Award #: N0001498WX30022

Dr. Brian J. Love
Dr. John Wallace Grant
Mr. Carvel Holton
Virginia Polytechnic Institute and State University
Department of Materials Science and Engineering
Blacksburg, VA 24061-0237
phone: (540) 953-1696

Dr. James Crivello
Rensselaer Polytechnic Institute
Department of Chemistry
110 8th Street
Troy, New York 12180-3590
phone: (518) 276-6825

LONG-TERM GOALS

The long-term goal of the research is to expand mission capabilities of Naval Special Warfare (NSW) in the underwater attachment of munitions and sensor packages on a variety of surfaces, quickly, covertly, and under extreme environmental conditions.

OBJECTIVES

The objective of this program is to investigate new technologies for adhering and attaching to surfaces underwater in conditions found throughout the world. The state of current attaching technology presently limits mission capabilities because of duration of cure or complete ineffectiveness in cold seawater temperatures. The primary thrust of this effort is to overcome conventional attaching technology limitations in providing NSW the capability to complete attaching tasks unrestricted of seawater conditions.

APPROACH

This program has been executed in several phases leading up to the current pursuit of multiple parallel approaches for underwater bonding. While it has been the intent of this program to meet all requirements¹, overcoming the primary technical obstacle of bonding quickly even in cold temperatures has been the primary thrust. In FY97 industry was solicited for both commercially off-the-shelf

Report Documentation Page

Form Approved
OMB No. 0704-0188

Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

1. REPORT DATE 1998		2. REPORT TYPE		3. DATES COVERED 00-00-1998 to 00-00-1998	
4. TITLE AND SUBTITLE Underwater Adhesives/Attachments				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Naval Surface Warfare Center, Coastal Systems Station Dahlgren Division, 6703 W. Highway 98, Panama City, FL, 32407				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES See also ADM002252.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 6	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

adhesives and proposals for developing new adhesive systems to meet NSW needs. No commercially available adhesives characterized or proposal evaluated were determined to meet NSW operational requirements. Multiple approaches have been pursued independently at the Naval Surface Warfare Center Dahlgren Division Coastal Systems Station (CSS), under contract with Dr. Brian Love, Dr. Wally Grant, and Mr. Carvel Holton of Virginia Polytechnic and State University (Virginia Tech), and under contract with Dr. James Crivello of Rensselaer Polytechnic Institute. As part of this program, the most appropriate technologies are to be identified for meeting operational requirements.

WORK COMPLETED


During the course of FY98, multiple technological approaches were pursued utilizing multiple sets of researchers in an attempt to increase the likelihood of success in identifying the most appropriate technology for meeting the requirements¹. The requirements determination incorporated and consolidated several different mission operational requirements into one document. Although all requirements produced are considered important, the primary thrust of this research effort is overcoming attachment performance in cold seawater temperatures. Through the course of this program, it has become evident that fulfilling these requirements will greatly expand Special Operations Forces (SOF) opportunities.

Work completed has consisted of conducting feasibility studies on various technologies including redox-curable epoxy adhesives, thermally assisted conventional adhesives, multi-pore (suction cup) attachment methods, photo-curable methacrylate adhesives, and photo-curable epoxies. As a result of FY98 research, it has been concluded that the photo-curable methacrylate and epoxy technologies investigated will easily satisfy adhesive strength evolution requirements in low temperature conditions. Several successful adhesive formulations have been produced as part of the effort.

RESULTS

Redox Curable Epoxy Adhesives

Efforts to develop a redox curable epoxy that would cure rapidly in near freezing water were conducted by Rensselaer Polytechnic Institute and is documented in "Photo- and Redox Curable Epoxy Adhesives for Underwater Applications"². The chemistry of the redox reaction is depicted below.

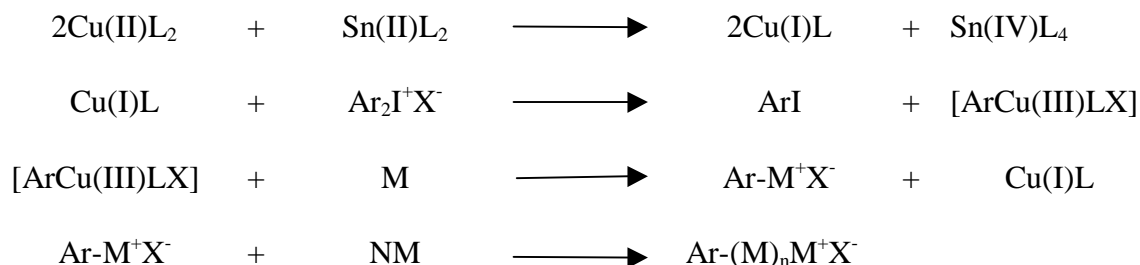

Despite the complex nature of this reaction, polymerizations are typically spontaneous, rapid and exothermic. Several formulations were developed in pursuit of a system that would satisfy the requirements. One such formulation is shown below.

Part A		Part B	
Vinylcyclohexene dioxide	2.4g	RG660 polyester	1.2g
IOC8 Initiator	0.5g	Coupling agent	0.3g
		Copper naphthenate	0.7g
		Stannous octoate	0.7g

In terms of reactivity, this system represents the highest attainable in a redox curable epoxy adhesive. When mixed at room temperature, the exotherm is so great that some of the monomer is vaporized. Underwater mixing produces steam. Attempts to cure the formulation in a 29° F water bath were made - the cure was observed to be very sluggish. Cure could only be obtained when a large mass of resin was present to provide sufficient exothermic heat to promote the reaction. Thin films of the adhesive would not cure in these cold water conditions. While the adhesive preformed well in ambient conditions, subsequent findings indicated a shelf-life stability issue with the copper catalyst. Over about a month period it was observed that the copper had reoxidized to form copper (II), which is inactive in the redox couple. Future efforts to formulate redox systems would need to address this stability issue. If the stability issue could be resolved, the redox system appears promising for in-air applications that require near-instant cure.

Thermally Assisted Conventional Adhesives

Virginia Tech investigated the potential of thermally assisted conventional adhesives to meet NSW requirements. The results of this effort are documented in “Energy Assisted Characterization of Marine Applications, Stage II - Heated Resin Feasibility Study”³. This effort was undertaken to determine whether it is feasible to heat commercially available adhesives in order to increase the reactivity of the adhesives to an acceptable level in near freezing seawater conditions. It was determined through modeling that thermal energy requirements are very much dependent on the substrate. Conductive substrates, such as steel (51.9 W/m- °C) and aluminum (200 W/m-°C) require an impractical amount of heat to increase the bond line reactivity to an acceptable level in near-freezing seawater conditions. Several exothermic chemical reactions were identified as candidates for possible future evaluation: AL/Fe Oxides and LiCl. In addition, experimentation was conducted by raising adhesive resin temperatures to a pre-set point (T_o) prior to submersion in water baths to determine the resulting conversion. Results indicated that the effects of the heat transfer to the surrounding water effectively terminated the reaction.

Photo-curable Methacrylate Adhesives

A photo-curable methacrylate, which would cure rapidly in near freezing water, was developed by Virginia Tech. This effort is documented in “Energy Assisted Adhesive Characterization for Marine Applications: Stage II - Light Curing Adhesive Feasibility Study”⁴. A methacrylate formulation was developed as part of this feasibility study (patent application is in process). The formulation utilizes camphorquinone as a light activated compound. The compound has a broad absorption with a maximum at a wavelength of approximately 470nm. The 470nm wavelength corresponds well with a blue LED that has been identified as a candidate irradiation source. Testing results to date indicate that the a single LED with adhesive will attach to substrates within two seconds at room temperature and five seconds in an ice bath. Additional efforts were made to produce an LED array for laboratory purposes that could be utilized to evaluate cure strength and cure rate of larger samples using LED's.

Testing to date has shown that at room temperature, 400 psi lap shear strengths using acrylic substrates can be produced within 30 seconds. Also, tensile tests of acrylic bonded to steel have shown results on the order of 200 psi within 30 seconds.

Photo-curable Epoxy Adhesives

A photo-curable epoxy which would cure rapidly in near freezing water was developed by Rensselaer Polytechnic Institute and is documented in “Photo- and Redox Curable Epoxy Adhesives for Underwater Applications”². Several photo-curable epoxy formulations that are UV curable were developed as a part of this effort. A few are shown below.

Entry	PC1000	Poly BD 605	ENR	SB Diblock	PBD Diol	Fume Silica	CHVE	DVE	Zonatac
1	-	-	-	-	30	02	40	-	25
2	65	20	-	-	10	02	-	-	-
3	65	05	-	-	25	02	-	-	-
4	65	30	-	-	-	-	-	-	-

Note: All amounts are given in parts by weight. All formulations contained 3 wt % coupling agent and 2 wt % triethyleneglycol for vinyl ether formulations, and 5 wt % IOC 8 photoinitiator.

During the course of this study, cure was demonstrated to occur within 60 seconds in an ice bath using a laboratory UV irradiation source. Lap shear strengths have been demonstrated to be > 320psi.

Multipore Suction Technology

A nonadhesive multipore suction technology was investigated by CSS and is documented in “Multipore Suction Technology”⁵. As part of this effort, numerous types and sizes of suction cups were evaluated on surfaces of varying roughness and geometries (fouled marine surfaces were not evaluated) in order to determine the best performing geometry. The ridged-backed type cups with elastomeric seals outperformed all other types of cups evaluated. Although several failures were experienced, attachment using a single cup was accomplished underwater for 24 hours. A benchtop multi-cup static system was developed to illustrate ways of providing redundancy and increasing the reliability of the attachment. In addition to determining the best performing cups, it was found that the addition of a viscous fluid (such as petroleum product) between the elastomeric seal and the substrate improved the overall performance of the cups.

Actuation technologies for a multipore system were also investigated as a part of this effort. These technologies included Ti-Ni (muscle wire), solenoid, and pneumatic systems. After initial considerations of the above technologies, it was decided that due to time constraints that the focus would be primarily on demonstrating a pneumatic algorithm. A benchtop pneumatic system incorporating a limit switch was developed. The system is capable of sensing release and resetting. It is conceivable that a system such as this could be miniaturized and adapted to a multiple component actuation system.

IMPACT/APPLICATIONS

Overcoming conventional environmental constraints of underwater bonding will expand forward military opportunities in addition to providing direction for future system developments that require bonding, both topside and underwater. This technology could have immediate application for the attachment of explosives and shaped charges, markers, an underwater diver pad-eye or for limpet mines.

TRANSITIONS

The technology is applicable to many Special Operations Forces (SOF) and Explosive Ordnance Disposal (EOD) mission scenarios. It is being transitioned for further development under shared funding from United States Special Operations Command and ONR's Surf Zone/Very Shallow Water (SZ/VSW) Mine Countermeasures (MCM) core program. It is expected to eventually transition to the VSW MCM Detachment in Coronado CA. Other fleet or commercial transitions are possible for applications that require quick bonding and attachment both in and above water.

RELATED PROJECTS

The Underwater Surface Preparation Technology Development Program begins in FY99. It will investigate/develop new technologies for preparing marine surfaces for adhesive bonding. Present attachment methods require at least minimal scraping that is unacceptable for some NSW applications.

REFERENCES

1. S.E. Gorin, "Underwater Adhesives and Non-Metallic Attaching Techniques Requirements," CSS/TN-96/7, Naval Surface Warfare Center Dahlgren Division Coastal Systems Station.
2. J. Crivello, 1998: "Photo- and Redox Curable Epoxy Adhesives for Underwater Applications," Rensselaer Polytechnic Institute.
3. B. Love, W. Grant and C. Holton, 1998: "Energy Assisted Characterization of Marine Applications, Stage II - Heated Resin Feasibility Study," Virginia Polytechnic Institute and State University.
4. B. Love, W. Grant and C. Holton, 1998: "Energy Assisted Adhesive Characterization for Marine Applications: Stage II - Light Curing Adhesive Feasibility Study," Virginia Polytechnic Institute and State University.
5. B. Courson and J. Shelburne, 1998: "Multipore Suction Technology," Naval Surface Warfare Center Dahlgren Division Coastal System Station.

PUBLICATIONS

Crivello, J., 1998: "Photo- and Redox Curable Epoxy Adhesives for Underwater Applications", Rensselaer Polytechnic Institute.

Love, B., Grant, W., and Holton, C., 1998: "Energy Assisted Characterization of Marine Applications, Stage II - Heated Resin Feasibility Study", Virginia Polytechnic Institute and State University.

Love, B., Grant, W., and Holton, C., 1998: "Energy Assisted Adhesive Characterization for Marine Applications: Stage II - Light Curing Adhesive Feasibility Study," Virginia Polytechnic Institute and State University.

Courson, B. and Shelburne, J., 1998: "Multipore Suction Technology," Naval Surface Warfare Center Dahlgren Division Coastal System Station, 1998.

PATENTS

Chemiluminescent - Photocurable Adhesive Curing and Bonding System; B. Courson, J. Wood and B. Love, Naval Surface Warfare Center Dahlgren Division Coastal Systems Station, Disclosure NC79295.

Light Cured Fiber Optic Splice Protectors and Components; C. Holton, R.O. Claus and B. Love, Virginia Polytechnic Institute and State University, Disclosure #98-017.

Method for Measuring the Strength Evolution of Fast Setting Adhesives; C. Holton, T. Kuhr and B. Love, Virginia Polytechnic Institute and State University, Disclosure #98-009.

Light Cured Adhesive for Marine and Civil Infrastructure Applications; B. Love, W. Grant, C. Holton, T. Kuhr and B. Courson, Virginia Polytechnic Institute and State University, Disclosure #98-008.
Patent pending.