

Ogden Air Logistics Center



U.S. AIR FORCE

Low Temperature Powder Coating

February 9, 2011

**ASETSDefense Conference
New Orleans, La**

Wayne Patterson

Hill AFB, Utah

801-775-2992

wayne.patterson@hill.af.mil

Report Documentation Page

Form Approved
OMB No. 0704-0188

Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

1. REPORT DATE 09 FEB 2011	2. REPORT TYPE	3. DATES COVERED 00-00-2011 to 00-00-2011			
4. TITLE AND SUBTITLE Low Temperature Powder Coating		5a. CONTRACT NUMBER			
		5b. GRANT NUMBER			
		5c. PROGRAM ELEMENT NUMBER			
6. AUTHOR(S)		5d. PROJECT NUMBER			
		5e. TASK NUMBER			
		5f. WORK UNIT NUMBER			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Ogden Air Logistics Center, Hill AFB, UT, 84056		8. PERFORMING ORGANIZATION REPORT NUMBER			
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)		10. SPONSOR/MONITOR'S ACRONYM(S)			
		11. SPONSOR/MONITOR'S REPORT NUMBER(S)			
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES ASETSDefense 2011: Sustainable Surface Engineering for Aerospace and Defense Workshop, February 7 - 10, 2011, New Orleans, LA. Sponsored by SERDP/ESTCP.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 26	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			



Overview



OGDEN AIR LOGISTICS CENTER

- **Current wet coating processes present environmental risks**
 - Results in the release of volatile organic compounds (VOCs) and hazardous air pollutants (HAPs)
 - Legacy primers contain hexavalent chrome
- **Conventional powder coatings result in an alternative highly durable coating**
 - Results in the release of volatile organic compounds (VOCs) and hazardous air pollutants (HAPs)
 - **Conventional powders cure at temperatures detrimental to some alloys**
- **Low Temperature Cure Powder Coating (LTCPC) is an alternative to conventional powder coating**
 - Cures at < 300 F
 - Still HAP/VOC free
 - Possibly formulated with corrosion inhibitors so chromated primers are not required



Project Team



OGDEN AIR LOGISTICS CENTER

	<p>Wayne Patterson OO-ALC 809 MXSS/CLA Hill AFB, UT</p>
	<p>Warren Assink AFRL Wright-Patterson AFB, OH</p>
	<p>David Piatkowski, Chris Mahendra NAVAIR</p>
	<p>James Davila, Chris Geib SAIC Beavercreek, OH</p>



TECHNICAL APPROACH



OGDEN AIR LOGISTICS CENTER

Demonstration Sites

Validation Phase

- Hill AFB, UT
- NAVAIR Pax River, MD
- CTC, Johnstown, PA
- NASA, Kennedy Space Center, FL

Evaluation Phase

- OO-ALC, Hill AFB, UT
- OC-ALC, Tinker AFB, OK
- WR-ALC, Robins AFB, GA
- NAS Whidbey Island, WA
- FRC Southwest, North Island, CA





Technical Objectives



OGDEN AIR LOGISTICS CENTER

- **The LTCPC Program was initiated with the following performance objectives:**
 - Demonstrate that LTCPC can show performance comparable to wet paint coatings in laboratory testing
 - Demonstrate that the LTCTC, as applied by trained coating personnel can withstand operational conditions as well as, or better than, wet paint coatings
 - Determine whether the use of LTCPC can result in process and/or environmental cost savings



TECHNICAL APPROACH




OGDEN AIR LOGISTICS CENTER

Powder Coating Technology

- Low Temperature Cure Powder Coating
 - Developed under SERDP Project WP-1268
 - Addressed deficiencies of conventional powder coatings
 - High curing temperatures
 - Long-term (>1000hrs) corrosion resistance

Equipment

- Corona Gun with adjustable voltage
 - Addresses limitation of conventional Corona Guns (Faraday Cage)
 - Improves uniformity of powder coverage within tight corners and recessed areas

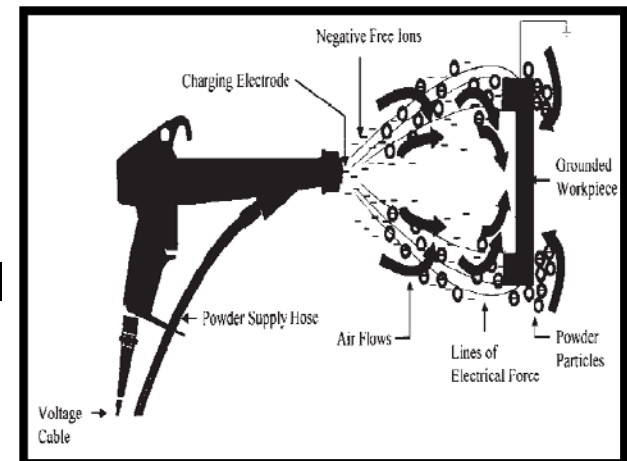




TECHNICAL APPROACH




OGDEN AIR LOGISTICS CENTER

Current Wet Coating Process

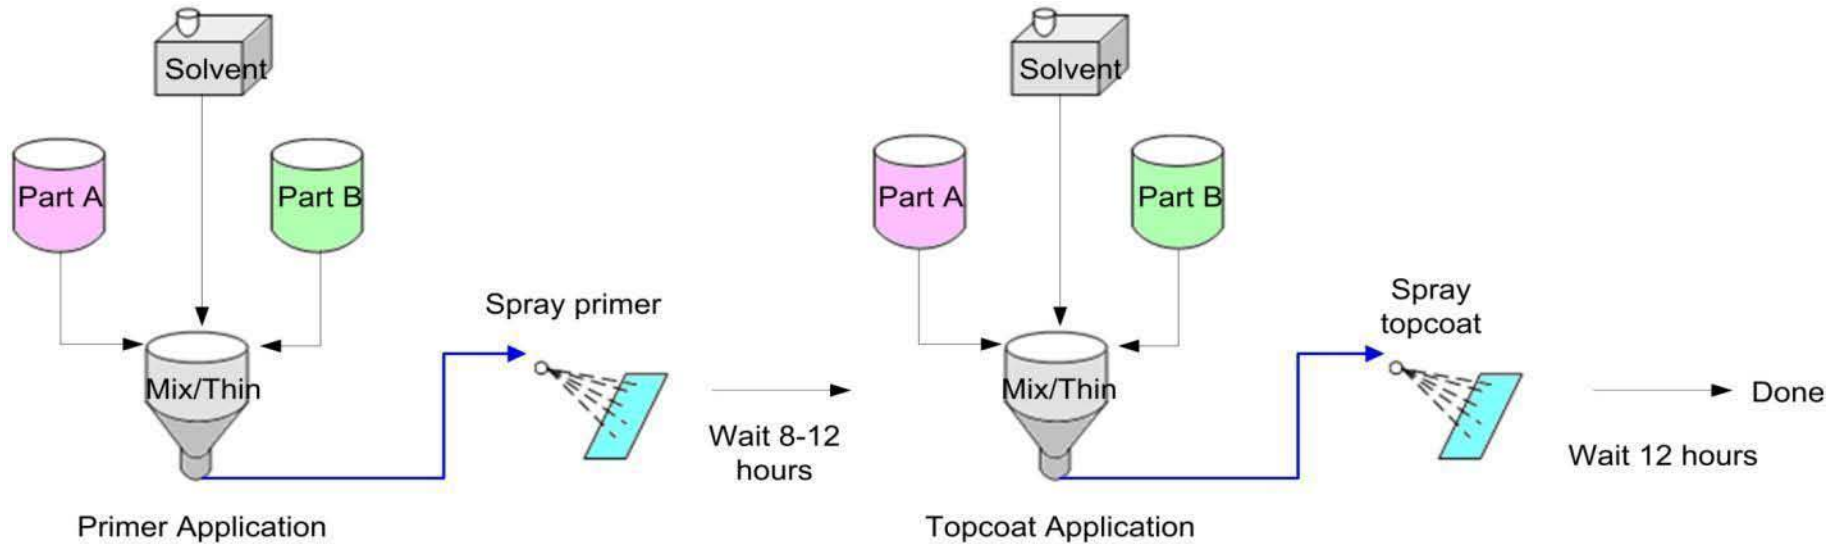

Proposed LTCP

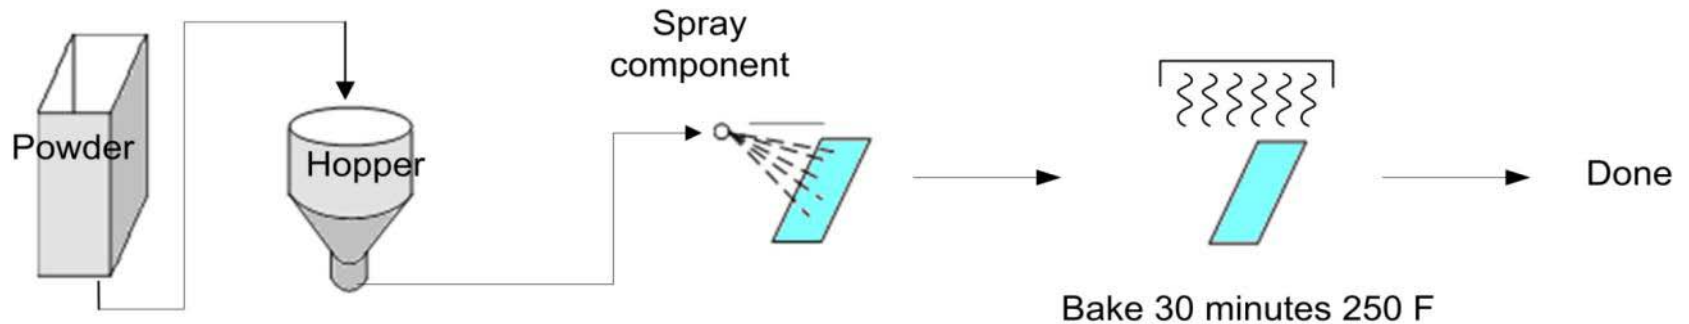



Powder Paint



OGDEN AIR LOGISTICS CENTER

Pros

- Storage / Shelf Life
- Single Component
- Quick
- Durable
- No VOC
- Transfer Efficiency 95%
- Waste is recyclable

Cons

- Small Parts (limited to booth & oven size)
- Geometries
- Must be cured at Temperature/Time
- Gas or Electric Oven




JTP Results




OGDEN AIR LOGISTICS CENTER

Filiform Corrosion Resistance

- LTCPC met requirements of MIL-PRF-23377 on two panels
- Third panel exhibited a single filament extending slightly beyond allowable tolerance

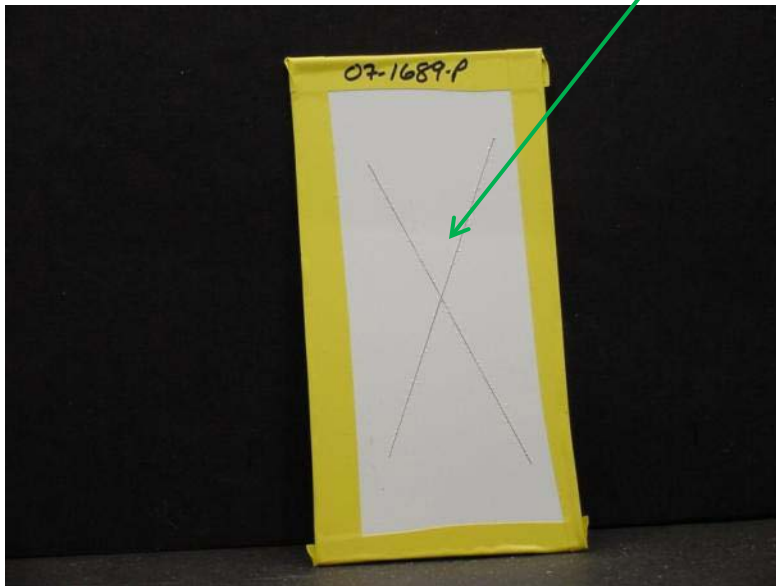

LTCPC on 2024 T-3 Clad

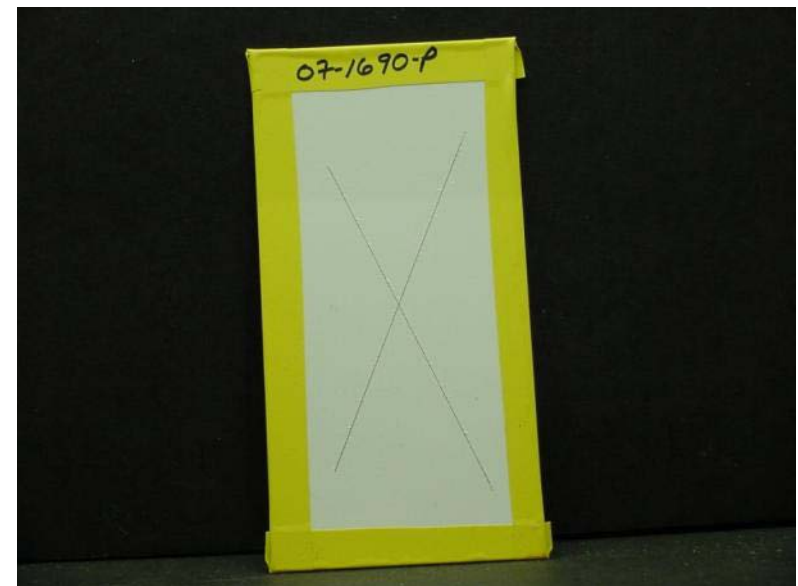

LTCPC on 2024 T-3 Clad





JTP Results



OGDEN AIR LOGISTICS CENTER

Neutral Salt Spray

- LTCPC performance similar or better than wet coating

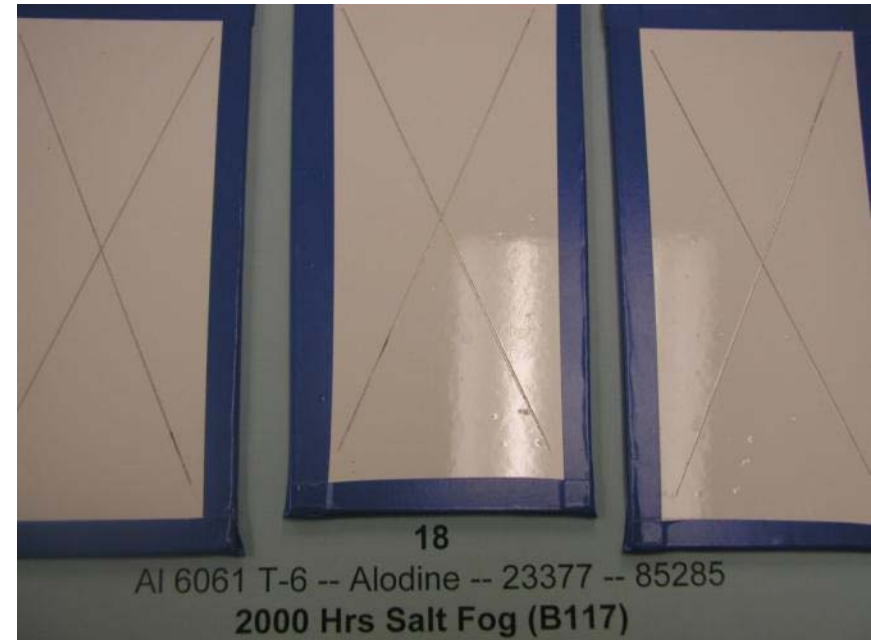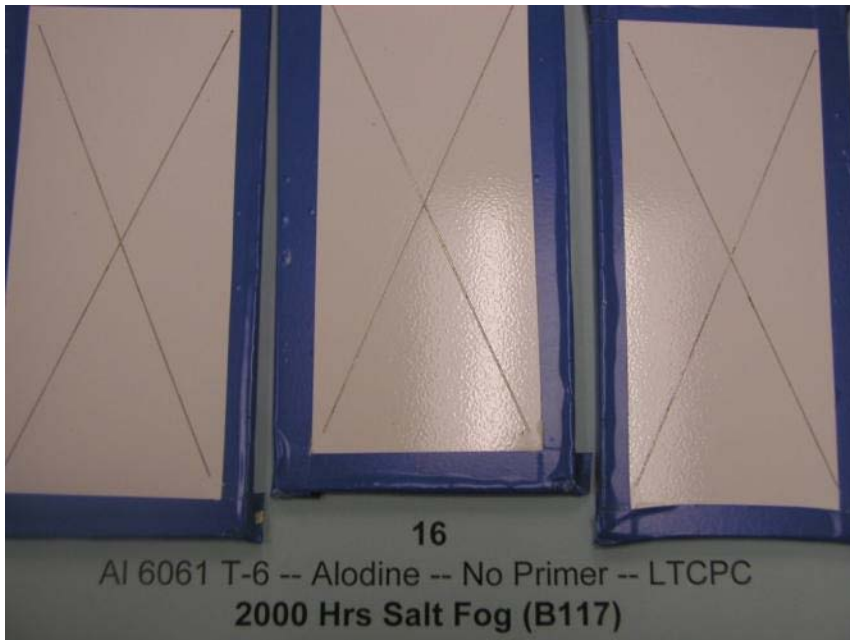




JTP Results




OGDEN AIR LOGISTICS CENTER

Flexibility / Impact Resistance

- LTCPC met requirements of MIL-PRF-23377 and MIL-PRF-85285

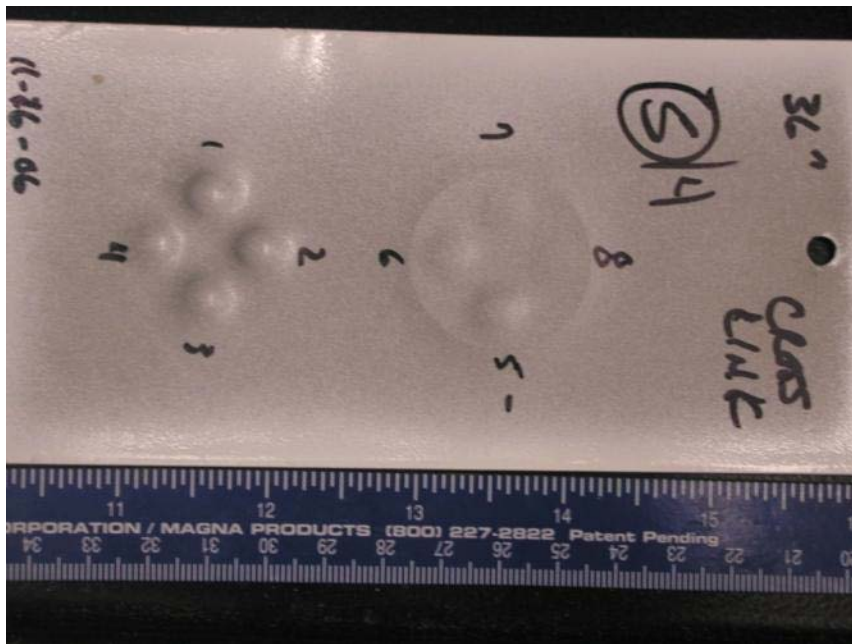

Back – LTCPC on 2024, 0 Temper Al

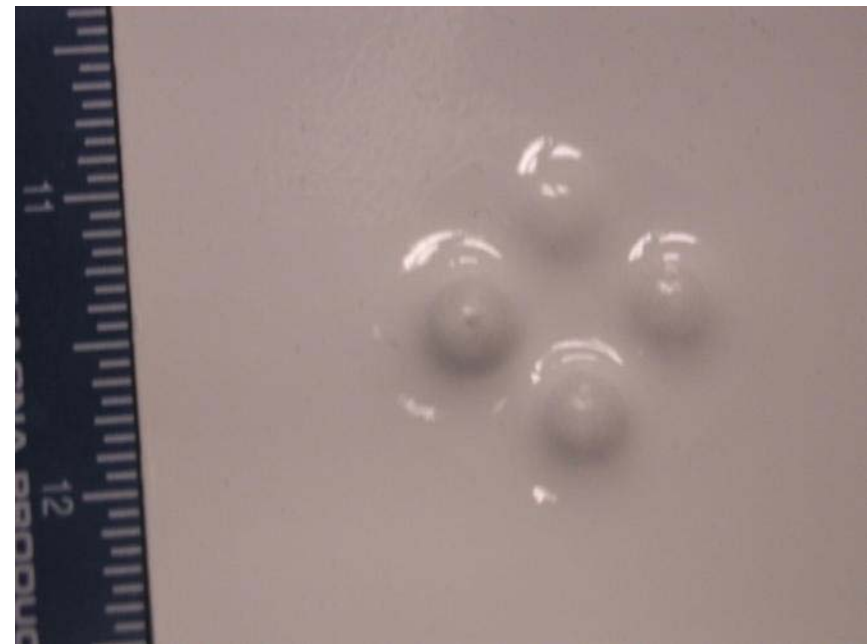

Front – LTCPC on 2024, 0 Temper Al




JTP Results



OGDEN AIR LOGISTICS CENTER

Adhesion Testing

- **LTCPC with pretreatment passed all adhesion testing**

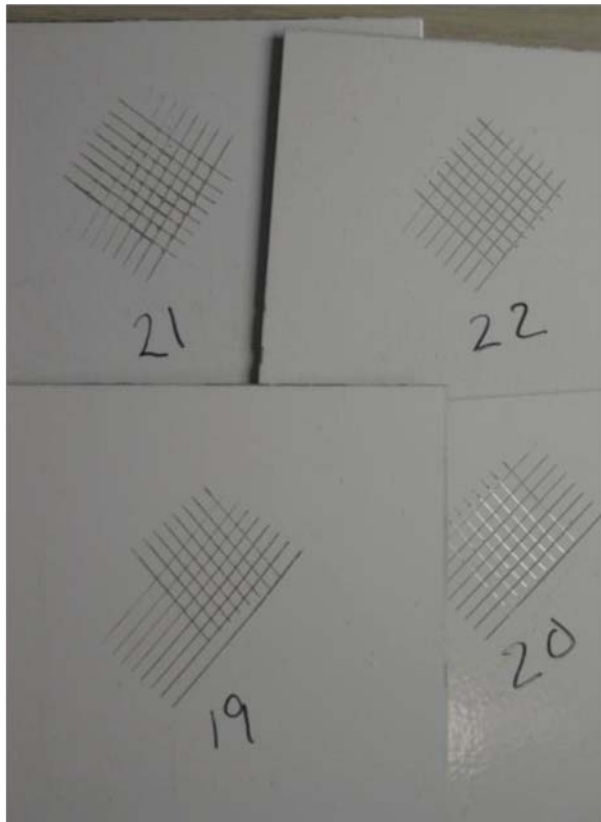

19. MIL-PRF-23377/MIL-PRF-85285 w/DOW 7 Pretreatment
20. LTCPC w/DOW 7 Pretreatment
21. LTCPC w/No Pretreatment (3b adhesion rating)
22. LTCPC w/DOW 7 and Prekote Pretreatment

(Magnesium Substrate, AZ31B)



JTP Results




OGDEN AIR LOGISTICS CENTER

Gravelometer



MIL-PRF-23377/85285

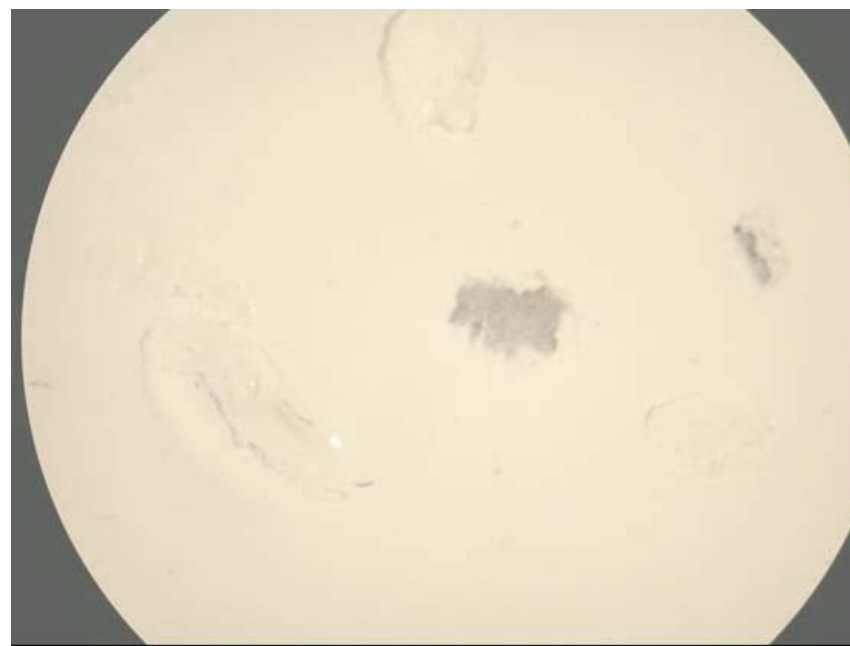

Powder Coat



JTP Results



OGDEN AIR LOGISTICS CENTER

Summary

WP-0614 LTCPC JTP Test Results

Substrate	Appearance	Salt Spray	SO2	Cyclic	Filiform	Adhesion	Impact	Strip	Immersion	Humidity	Gravel	Low T Flex
4130 steel	SAME	SAME	SAME	SAME	--	SAME	--	Note 3	--	--	--	--
2024-T0 Al	SAME	--	--	--	--	--	Note 2	--	--	--	--	Note 2
2024-T3 Al (CCC)	SAME	SAME	SAME	--	--	--	--	--	Note 2	Note 2	--	--
2024-T3 Al (No)	SAME	LESS	LESS	--	--	--	--	--	Note 2	Note 2	Note 2	--
6060-T6 Al (CCC)	SAME	SAME	SAME	--	--	--	--	--	--	--	--	--
6060-T6 Al (No)	SAME	LESS	LESS	--	--	--	--	--	--	--	--	--
2024-T3 Clad (CCC)	SAME	SAME	--	BETTR	Note 1	--	--	--	--	--	--	--
2024-T3 Clad (No)	SAME	LESS	--	SAME	--	--	--	--	--	--	--	--
6061-T6 Al (CCC)	SAME	BETTR(note 4)	SAME	--	--	SAME	--	Note 3	--	--	--	--
6061-T6 Al (PK)	SAME	BETTR (note 4)	LESS	--	--	SAME	--	Note 3	--	--	--	--
AZ31B Mg (Dow)	SAME	SAME	--	--	--	SAME	--	Note 3	--	--	--	--

Legend: LESS=Less than control SAME=Same as control BETTR=Better than control

Note 1: Two of three LTCPC panels passed. One panel exceeded limit by 1/32 in.

Note 2: Met requirements in the MIL Standards (MIL-PRF-23377, MIL-PRF-85285, MIL-PRF-24712)

Note 3: Non methylene chloride stripper effective.

Note 4: Exceeded 3300 hrs in salt spray

BE AMERICA'S BEST







Demonstration Testing



OGDEN AIR LOGISTICS CENTER

- **USAF & USN Demonstration Sites & Test Articles**
 - **NAS Whidbey Island, WA**
 - Depot for majority of the LTCPC Navy Demo GSE
 - Engine Yokes
 - Partial results collected on tow bars, pod cradles, and bomb hoists, but coating was stripped early due to NDE requirements
 - **NAS North Island, CA**
 - Maintenance facility for GSE deployed on the USS Ronald Reagan
 - Nitrogen Carts
 - **OO-ALC, Hill AFB, UT**
 - C-130 forward landing gear doors
 - C-130 Throttle Quads



Results - Demonstration Testing



OGDEN AIR LOGISTICS CENTER

- Navy Ground Support Equipment Field Service Evaluation – NAN-4 Nitrogen Servicing Cart





Results - Demonstration Testing



OGDEN AIR LOGISTICS CENTER

- **Navy Ground Support Equipment Field Service Evaluation – J-52 Engine Yoke Adapters**



BE AMERICA'S BEST



Results - Demonstration Testing



OGDEN AIR LOGISTICS CENTER

- Air Force Field Service Evaluation – C-130 Nose Landing Gear Doors (Interior Surfaces)



Chromate CC LTC Powder

BE AMERICA'S BEST



C-130 Landing Gear Door



OGDEN AIR LOGISTICS CENTER



BE AMERICA'S BEST




HILL ROM
FOR REPAIR CONTACT
SARGENT CHRIS COMLEY
DSN 388-6363



C-130 Throttle Quads



OGDEN AIR LOGISTICS CENTER

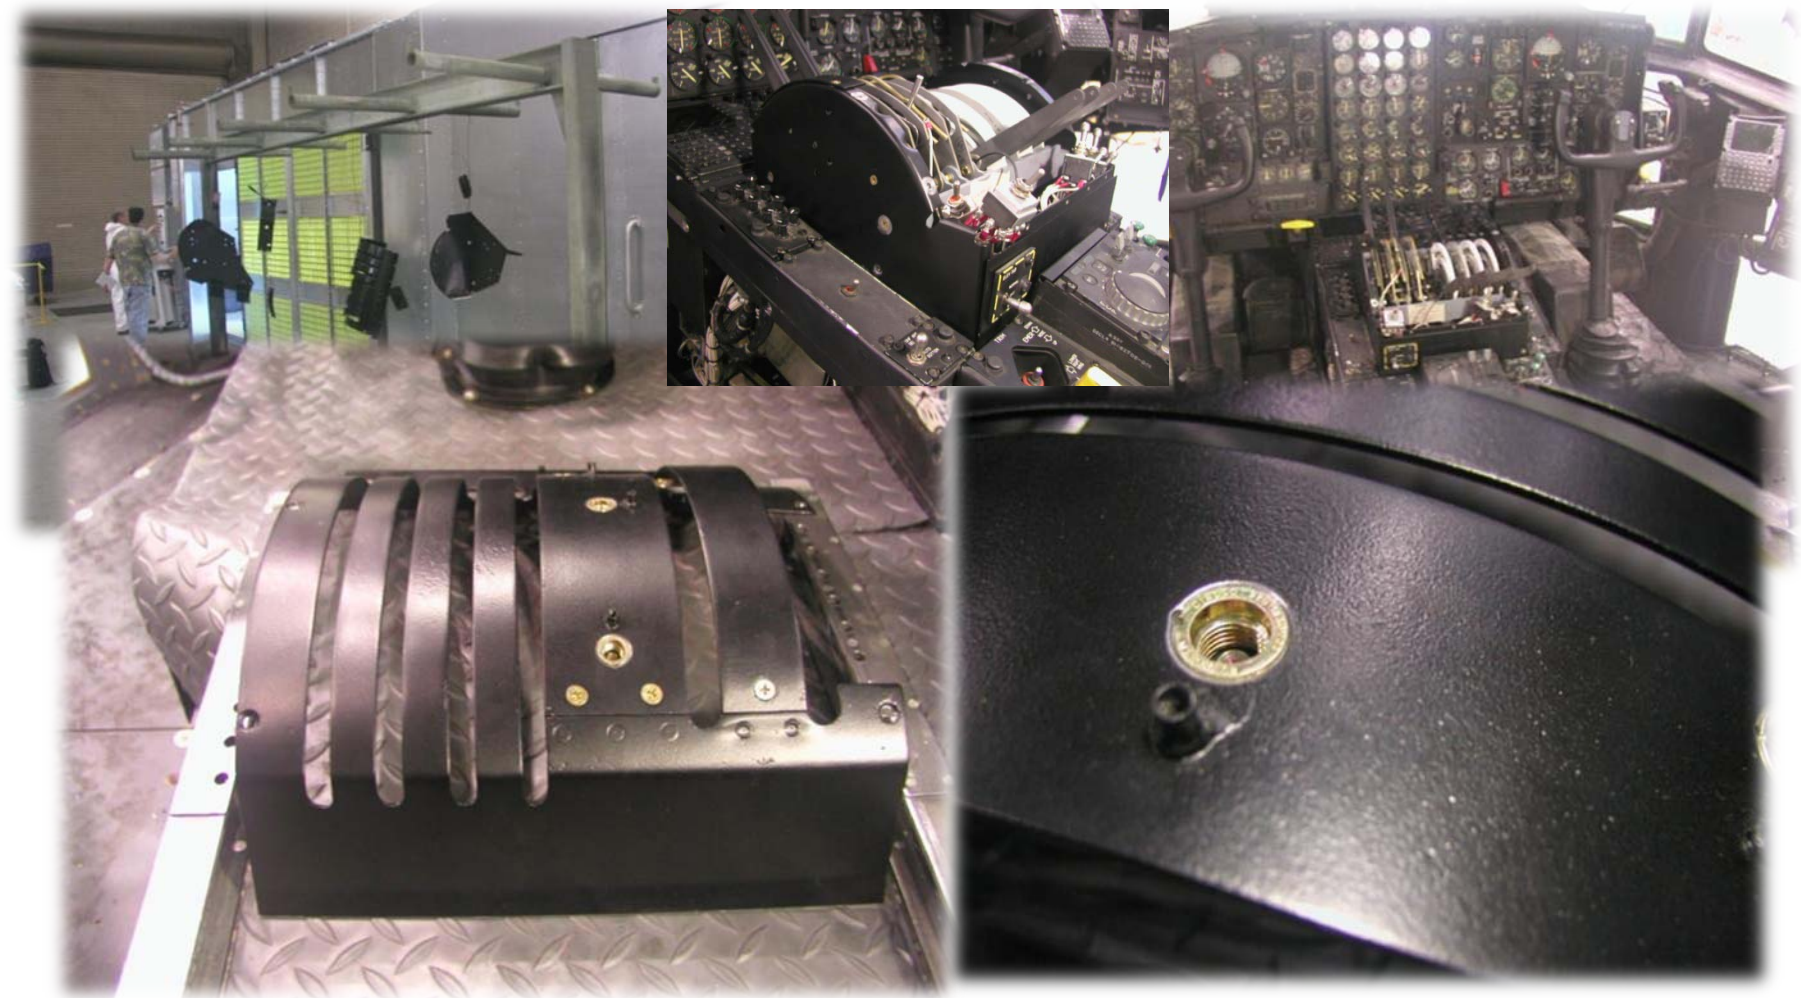

BE AMERICA'S BEST



Conclusions and Summary



OGDEN AIR LOGISTICS CENTER

- **Low Temperature Cure Powder Coatings performs comparably to conventional wet coatings both in laboratory and field service evaluations**
- **LTCPC allows environmental cost reductions through VOC/HAP elimination and hexavalent chrome reduction.**
- **The LTCPC process greatly shortens the coating operation (LTCPC cures much more rapidly than conventional wet coatings) resulting in labor savings and improved part processing rates.**



Conclusions and Summary



OGDEN AIR LOGISTICS CENTER

- **Powder Coatings are not a total replacement for wet paints...However they are a viable replacement for quite a few back shop processes**
 - **Be observant and cognoscente of processes**
 - **Don't be afraid to try it...Use the Correct Procedure... get authorizations**
 - **Document successes and failures**
- **New Powders are being Developed as Industry sees *the Need and possibilities of use.***



PUBLICATIONS



OGDEN AIR LOGISTICS CENTER

Geib, C.W., Davila J.A., Patterson W., et al. "Low Temperature Cure Powder Coating, ESTCP Project WP-0614." Joint Services Environmental Management Conference, Columbus, Ohio. 21 – 24 May 2007.

Geib, C.W., Davila J.A., Patterson W., et al. "Advances and Testing of Powder Coatings for Aerospace Applications, ESTCP Project WP-0614." SAE AMS Aerospace Organic Coatings Committee (AMS G-8) Fall 2007 Meeting, Long Beach, California. 6 Nov 2007

WP-0614 – Low Temperature Cure Powder Coatings. Poster. The Partners in Environmental Technology Technical Symposium & Workshop. Patterson, W., Davila J.A., et al. Washington, DC. Dec 2007.

Geib, C.W., Davila J.A., Patterson W., et al. "Environmentally Advantaged Powder Coatings for Aerospace Applications." Third Annual Advanced Aerospace Coating/Decoating Technical Symposium, Orlando, Florida. 9,10 Jan 2008.

Geib, C.W., Davila J.A., Patterson W., et al. "Environmentally Advantaged Powder Coatings for Aerospace Applications, ESTCP Projects WP-0614 & WP-0801." SERDP/ESTCP Workshop on Surface Finishing and repair Issues for Sustaining New Military Aircraft, Tempe, Arizona. 26-28 Feb 2008.