

U. S. NAVAL PROVING GROUND  
DAHLGREN, VIRGINIA



UNCLASSIFIED

REPORT NO. 7-45

MASTER COPY

NPG 7-45

ci

AD-310007

EXAMINATION OF ITALIAN PROJECTILES

47mm A.P. PROJECTILE

47mm H.E. PROJECTILE

105mm H.E. PROJECTILE

120mm COMMON PROJECTILE

149mm H.E. PROJECTILE

6" H.E. PROJECTILE

6" COMMON PROJECTILE

*Dist. Statement A -  
Approved for Public Release*

INDEXED	✓
DESCRIPTIVE	✓

UNCLASSIFIED

ON 8-10-76  
(DATE)

BY AUTHORITY OF *M. Verus*  
(SIGNATURE)

(CHANGED TO) *NAVORD ITR 8652478-RAM*  
5511 dtd 31 Oct 73  
(RANK)

July 1945

UNCLASSIFIED

TECHNICAL LIBRARY FILE COPY

UNCLASSIFIED

NPG 7-45

87 9 1 172

Encl. (13)

NOTICE OF CHANGE IN CLASSIFICATION  
OPNAV FORM 5511-11 (4-56) S/N C107-786-1000

COMMANDER

ORIGINATOR OR HIGHER AUTHORITY HAVING COGNIZANCE OVER SUBJECT MATTER

NAVY SURFACE WEAPONS CENTER  
DAHLGREN LABORATORY  
DAHLGREN, VIRGINIA 22448

DATE

9 SEP 1976

ADDRESSEES OF ORIGINAL DISTRIBUTION (Use Standard Navy Distribution List numbers if applicable. Additional sheets may be attached if more space is necessary.)

The material described below has been changed in classification as indicated. Addressees shall change the classification of copies held.

REGRADED TO \_\_\_\_\_

DOWNGRADED TO \_\_\_\_\_


DECLASSIFIED

DATE AND DESCRIPTION OF MATERIAL (Avoid identification which would cause this form to be classified.)

NPG Report No. 7-45, July 1945, Subj: Examination of Italian Projectiles(U)

REMARK WITH DISTRIBUTION STATEMENT "A" - Approved for Public Release;  
Distribution Unlimited

SIGNATURE OF AUTHORIZING OFFICIAL

  
C. W. PHILBRICK, Security Supervisor  
By direction

U. S. NAVAL PROVING GROUND  
DAHLGREN, VIRGINIA

UNCLASSIFIED

July 1945

REPORT NO. 7-45

EXAMINATION OF ITALIAN PROJECTILES

- 47mm A.P. PROJECTILE
- 47mm H.E. PROJECTILE
- 105mm H.E. PROJECTILE
- 120mm COMMON PROJECTILE
- 149mm H.E. PROJECTILE
- 6" H.E. PROJECTILE
- 6" COMMON PROJECTILE

CLASSIFICATION (CHANGED TO) [REDACTED] (RANK) 73  
UNCLASSIFIED BY AUTHORITY OF NAVY ORD 06521478-2 PPM  
ON 8-10-76 BY [REDACTED] 2511 [REDACTED] 31 [REDACTED]  
(DATE) (SIGNATURE)

INDEXED	
DESCRIPTIVE	

APPROVED:



K. M. MCLAREN  
CAPTAIN, U. S. N.  
ACTING COMMANDING OFFICER

UNCLASSIFIED

UNCLASSIFIED

PREFACE

AUTHORIZATION

Specific directives for these investigations were issued in BuOrd ltr. EF 74(Re3) dated 23 December 1944 and BuOrd ltr. EF 74(Re3) dated 26 February 1945.

OBJECT

To make a complete physical, chemical and metallurgical examination of the following Italian projectiles.

47mm A.P. Projectile  
47mm H.E. Projectile  
105mm H.E. Projectile  
120mm Common Projectile  
149mm H.E. Projectile  
6" H.E. Projectile  
6" Common Projectile

UNCLASSIFIED

UNCLASSIFIED

INDEX

SECTION

- I EXAMINATION OF ONE ITALIAN 47mm A.P. PROJECTILE
- II EXAMINATION OF ONE ITALIAN 47mm H.E. PROJECTILE
- III EXAMINATION OF ONE ITALIAN 105mm H.E. PROJECTILE
- IV EXAMINATION OF ONE ITALIAN 120mm COMMON PROJECTILE
- V EXAMINATION OF ONE ITALIAN 149mm H.E. PROJECTILE
- VI EXAMINATION OF ONE ITALIAN 6" H.E. PROJECTILE
- VII EXAMINATION AND BALLISTIC TESTS OF ITALIAN 6"  
COMMON PROJECTILES

UNCLASSIFIED

UNCLASSIFIED

I

EXAMINATION OF ONE ITALIAN 47mm.

A.P. PROJECTILE

CEE NO. 3662

SUMMARY

This projectile was made from nickel, chromium, silicon steel. It was forged and machined, then heated uniformly and quenched and drawn. The base was drawn in a separate operation to a low hardness. - A hardness survey of the entire projectile was made.

The chemical analyses and microstructure of all the projectile components are given.

UNCLASSIFIED

UNCLASSIFIED

CONTENTS

		<u>Page</u>
I.	INTRODUCTION . . . . .	1
II.	EXAMINATION - Physical, Chemical, Metallurgical . .	1
III.	DISCUSSION . . . . .	2


LIST OF FIGURES

		<u>Opposite</u> <u>Page</u> -----
Fig. 1	NPG Photo No. 2270 (APL) As Received and Disassembled View . . . . .	1
Fig. 2	NPG Photo No. 2548 (APL) Markings on Projectile and Case . . . . .	1
Fig. 3	NPG Photo No. 2546 (APL) Hardness Distribution and Macro-section. . . . .	2
Fig. 4	NPG Photo No. 2649 (APL) Microstructures . . .	2
Fig. 5	NPG Photo No. 2650 (APL) Microstructures . . .	2


UNCLASSIFIED

Figure 1

NFG Photo No. 2270 (APL)  
As received and disassembled view of Italian 47mm A.P.  
round. CEE No. 3662.  
15 May 1945



UNCLASSIFIED

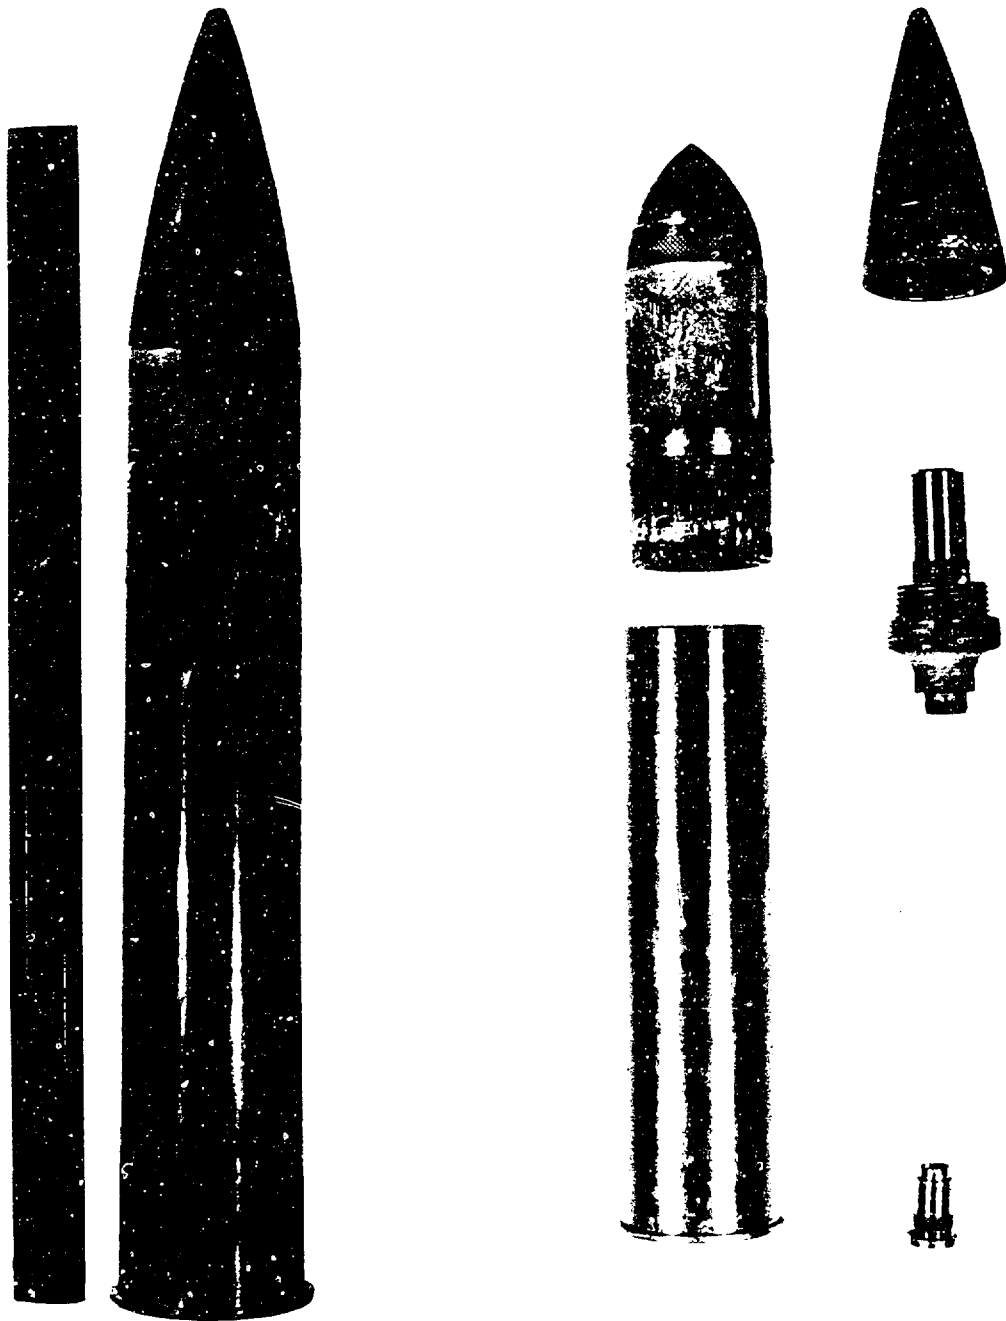


UNCLASSIFIED



Figure 2  
MARKINGS ON ITALIAN 47mm AP  
PROJECTILE AND CASE

UNCLASSIFIED

CEE 3662

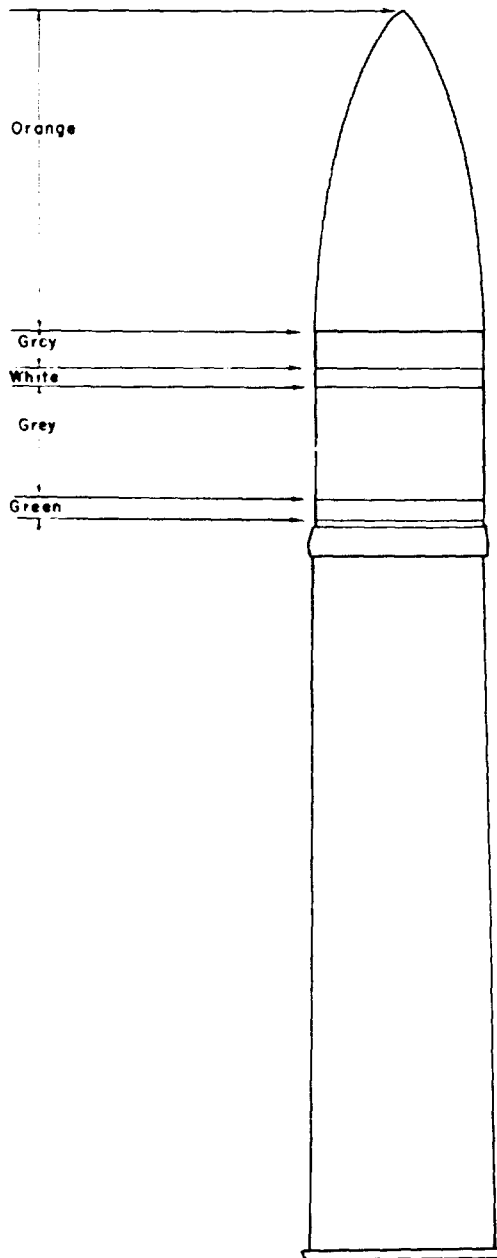

Stenciled


T-P  
DOG. 39

Stamped

B-T

Indistinct Stenciling

Carica da 47 P. Poiv.  
P.C. 3-0, 75x8x110x140 Dr. 173  
4069008-'941'  
DIREZ. D'ARTIGL.-PIACENZA  
NOVEMBRE 9'41



All Markings  
Stamped

UNCLASSIFIED

## I. INTRODUCTION

One Italian 47mm A.P. round was received at the Naval Proving Ground for complete physical, chemical and metallurgical examination. The following is a report of this investigation in accordance with the directives.

II. EXAMINATION  
PHYSICAL

The complete round, as received and disassembled is shown in Figure 1. The projectile is provided with a windshield which is crimped to the nose and with a base plug carrying a base detonating fuze and tracer. The markings found on the round are reproduced in Figure 2. These markings show that the case was manufactured in 1941 but give no indication as to the date of manufacture of the projectile. Colors used to identify the projectile and its loading are also shown in Figure 2.

## CHEMICAL

Chemical analyses of the projectile components are given in the following table. Steel analyses are spectrochemical excepting carbon, phosphorus and sulphur which have been obtained by standard wet chemical methods.

	C	Mn	P	S	Si	Ni	Cr	Mo	Cu	Al
Windshield	.07	.35	.007	.036	NTr	<.08	NTr	.02	Tr	Tr
Body	.50	.53	.027	.022	1.23	.62	.80	.02	.18	NTr
Base Plug	.36	.62	.015	.014	.29	<.08	NTr	<.005	Tr	NTr
	Cu	Zn	Sn	Fe	P					
Band	99.78	.035	.035	.120	.024					

Tr = Trace

NTr = No Trace

The windshield has been fabricated from a low carbon rimmed steel of the type commonly used for the manufacture of thin sheet to be used for deep drawing. A nickel, chromium, silicon steel has been used for the body of the projectile and the base plug is manufactured from a medium carbon steel similar to SAE 1035. The rotating band is copper but is rather impure as compared to American standards for this material.


UNCLASSIFIED

Figure 3

# HARDNESS DISTRIBUTION AND MACROSECTION OF ITALIAN 47mm AP PROJECTILE


Hardness Values: Vickers Pyramid (50 Kg.)  
Etch: Ammonium Persulphate

GEE 3662

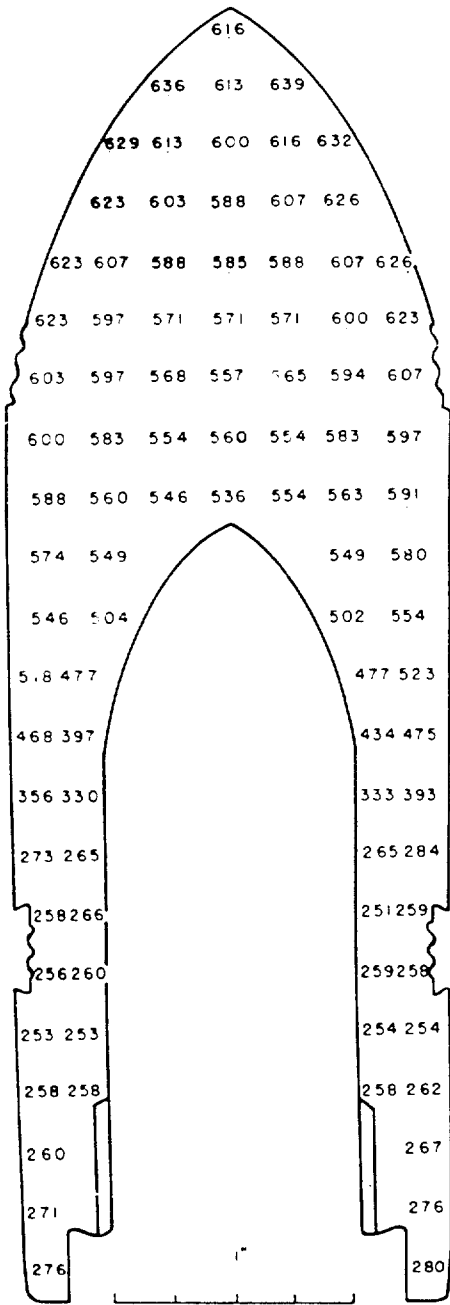

Scale

NFG Photo No. 2546 (APL)  
May 15, 1945

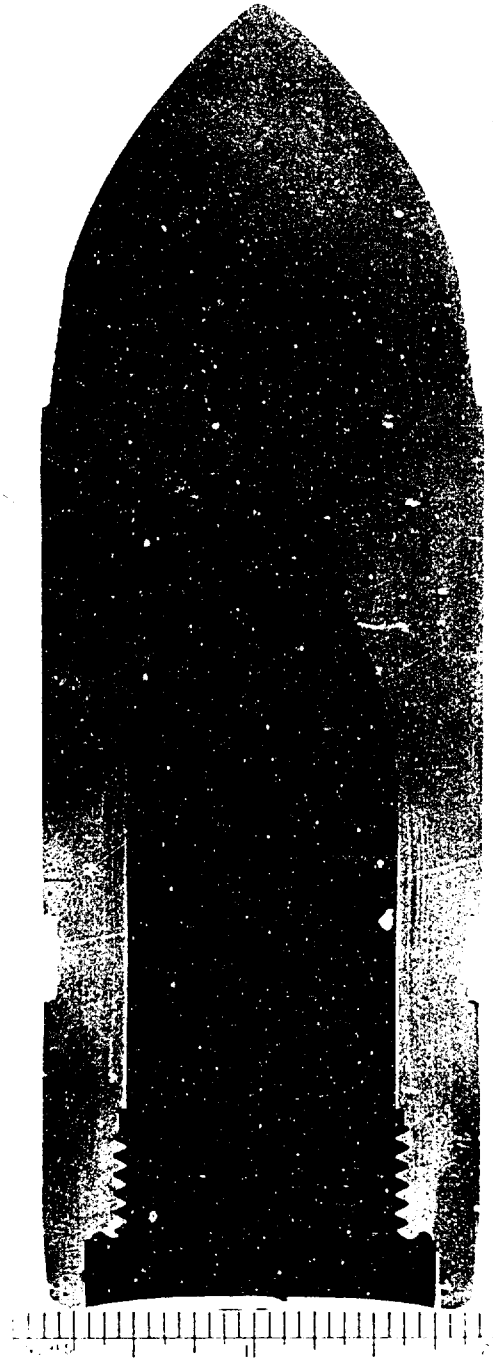

UNCLASSIFIED  
AS APPL

UNCLASSIFIED

Figure 4

MICROSTRUCTURES OF  
ITALIAN 47mm AP PROJECTILE



PROJECTILE NOSE Martensite  
with Bainite Needles

Hardness - 610 VPN  
Magnification - 1000X  
Etch - Picral Nital  
M489



PROJECTILE BASE Tempered  
Martensite


Hardness - 260 VPN  
Magnification - 1000X  
Etch - Picral Nital  
M490

NPG Photo No. 2649 (APL)  
15 June 1945  
~~XXXXXXXXXX~~

UNCLASSIFIED

Figure 5

MICROSTRUCTURES OF  
ITALIAN 47mm AP PROJECTILE

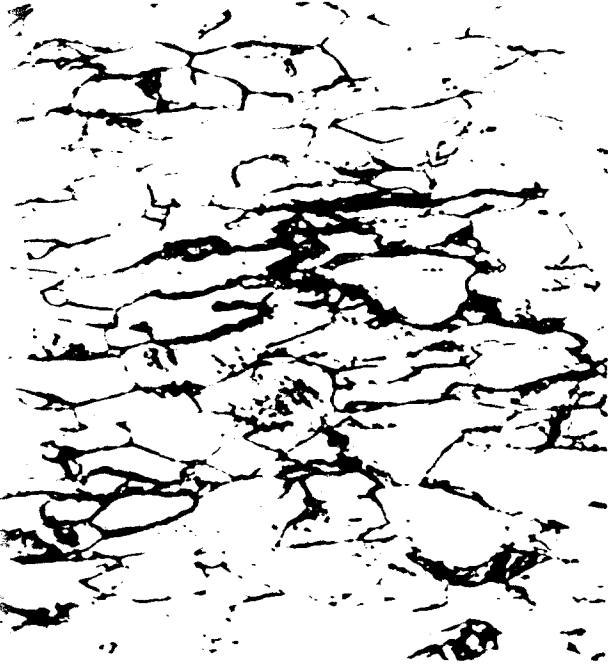

WINDSHIELD Ferrite

Hardness - 79 Rb  
Magnification - 250X  
Etch - Nital  
M492



BASE PLUG Pearlite and  
Ferrite

Hardness - 85 Rb  
Magnification - 250X  
Etch - Picral  
M491

NPG Photo No. 2650 (AFL)  
15 June 1945

UNCLASSIFIED

## METALLURGICAL

The projectile body was split longitudinally with an abrasive cut-off wheel and a hardness survey made of the entire cross-section. Figure 3 shows the hardness distribution and macro-etch section of the body. A maximum hardness of approximately 630 VPN (56Rc) has been obtained on the nose of the projectile. The hardness drops off slowly from the nose to a point about a quarter of an inch above the band score where it drops off rapidly to approximately 260 VPN (25Rc) which hardness is maintained throughout the base. The flow lines shown in the macro-etch section indicate that the projectile was forged and machined.

The microstructure of the nose and base of the projectile are shown in Figure 4. Both structures were produced by a normal quench and temper operation, the nose consisting of martensite and bainite and the base, tempered martensite. The microstructures of the other components of the projectile are shown in Figure 5. The windshield is seen to consist of ferrite with perhaps a slight trace of pearlite, while the base plug has a normalized structure of pearlite and ferrite. The hardness of these two components was found to be as follows:

Windshield - - - -	79 Rb
Base Plug - - - -	85 Rb

## III. DISCUSSION

The maximum nose hardness of this 47mm projectile is somewhat lower than the nose hardness of American projectiles of this caliber. The American 37mm and 40mm AP projectiles generally have a nose hardness of from 700 to 750 VPN (60 to 62 Rc), as compared to approximately 630 VPN (56Rc) for the subject projectile.

An examination of the photomicrographs and etch section of this projectile indicate that it was probably heat treated in the following manner.

- (a) Heated uniformly to above its critical temperature and quenched
- (b) Drawn at a temperature to produce a hardness of approximately 630 VPN (56Rc)
- (c) Base drawn in lead at a temperature between 1100 and 1200° F.

UNCLASSIFIED

II  
EXAMINATION OF ONE ITALIAN 47mm  
H.E. PROJECTILE  
CEE NO. 3662

SUMMARY

The projectile body was machined from a sulphur bearing plain carbon steel. It was given a single normalizing heat treatment, and has a uniform hardness of approximately 92 R<sub>B</sub>.

The chemical composition and microstructure of the projectile are given.

UNCLASSIFIED

UNCLASSIFIED

CONTENTS

	<u>Page</u>
I. INTRODUCTION . . . . .	1
II. EXAMINATION - Physical, Chemical, Metallurgical . . .	1
III. DISCUSSION . . . . .	2

LIST OF FIGURES

	<u>Opposite Page</u> -----
Fig. 1 NPG Photo No. 1850 (APL) As Received and Disassembled View . . . . .	1
Fig. 2 NPG Photo No. 2443 (APL) Markings on Projectile and Case . . . . .	1
Fig. 3 NPG Photo No. 2594 (APL) Deep Etched Section .	1
Fig. 4 NPG Photo No. 2651 (APL) Microstructure. . . .	1

UNCLASSIFIED

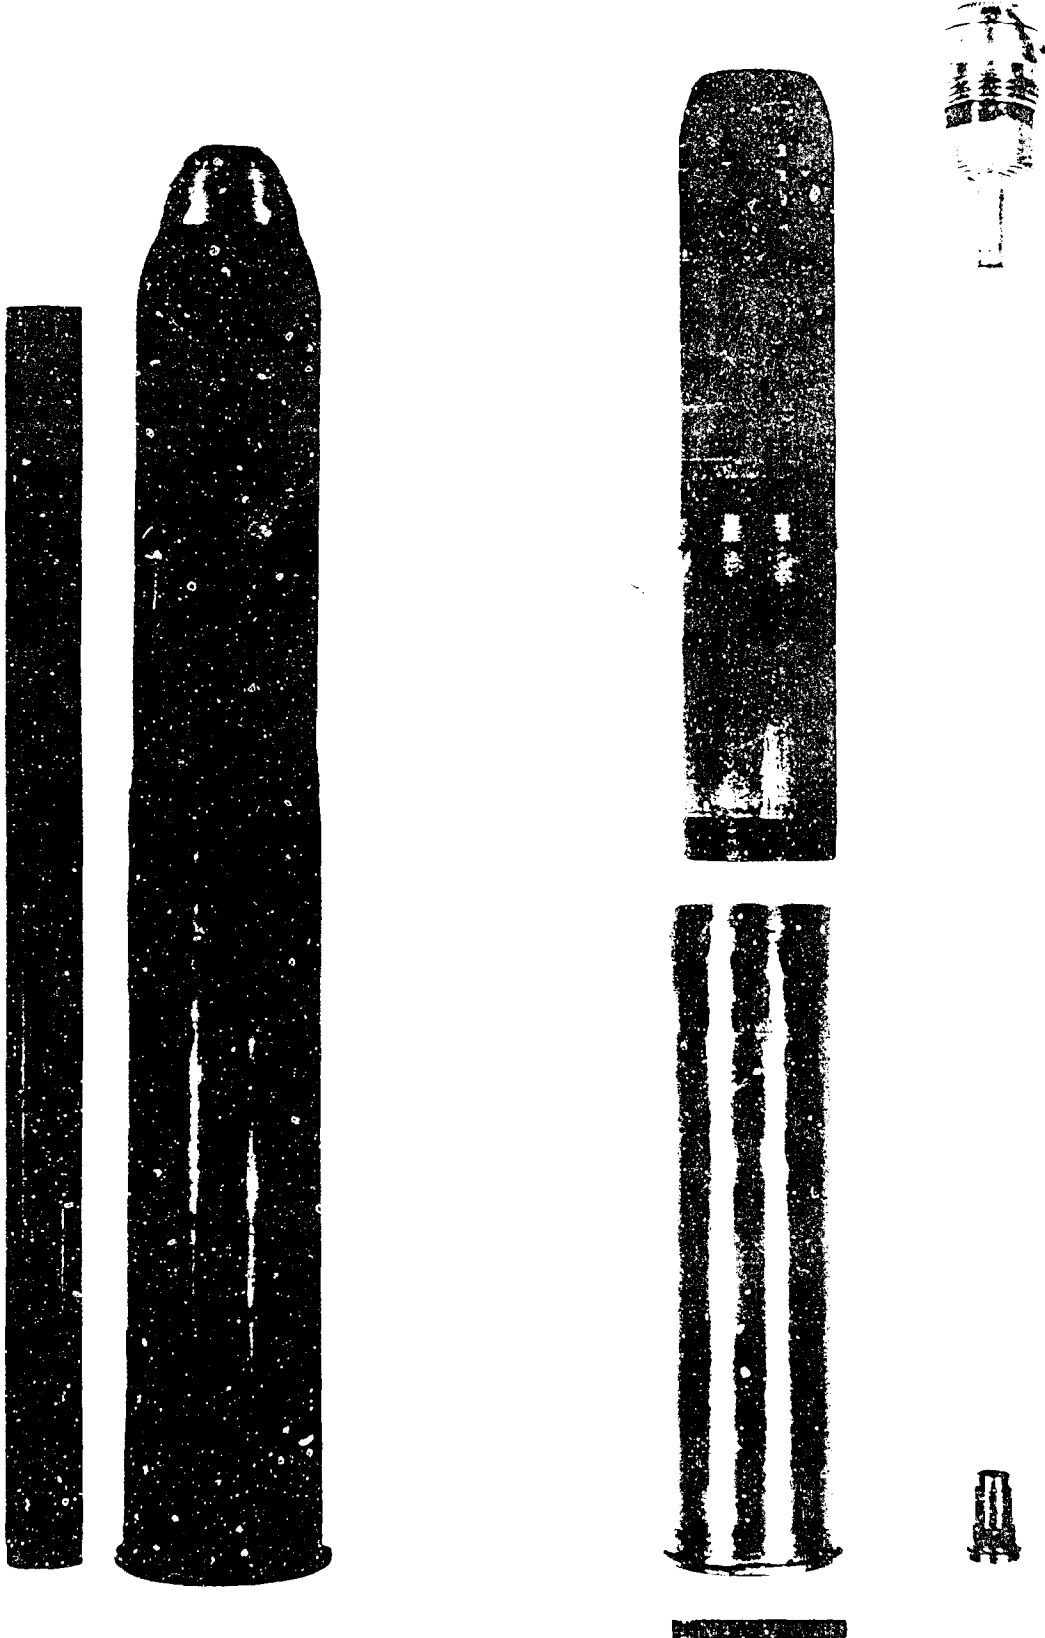


Figure 1

NFG Photo No. 1350 (APL).  
As received and disassembled view of Italian 4.7mm H.E.  
round. CBE No. 3662.  
15 May 1945



UNCLASSIFIED




UNCLASSIFIED


UNCLASSIFIED

Figure 2  
MARKINGS ON ITALIAN  
47mm HE PROJECTILE

CEE 3662

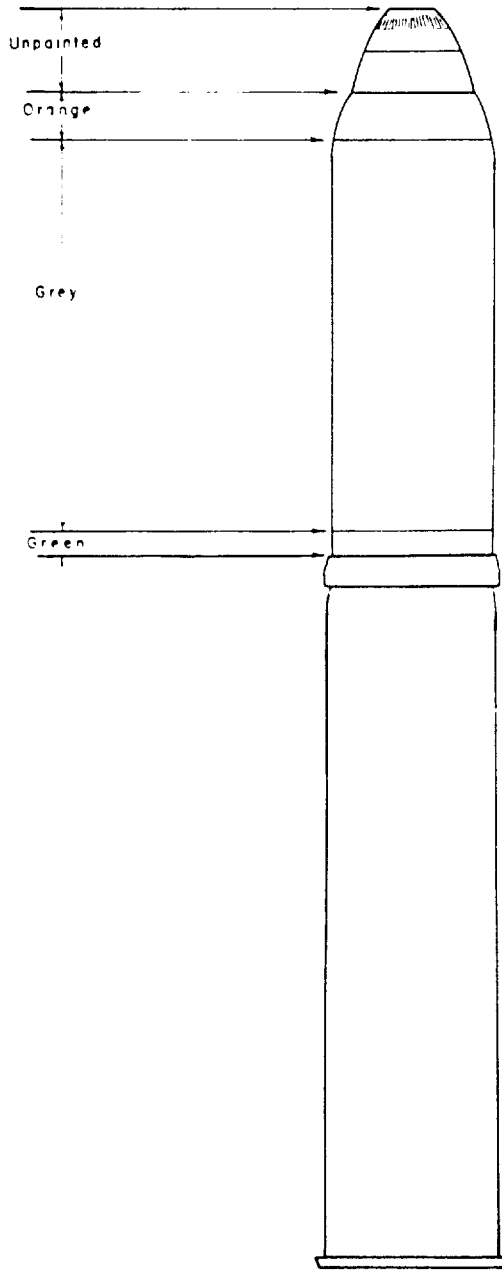

Stamped on Fuze



Stenciled

2 340

TRETOLO


47

Industrial Stenciling

Carica da 47/32 Pov. P.C. 403

Mat. 405:011/1940

DIREZ ONE ARTIGLIERIA BOLOGNA 1940



All Markings  
Stamped

UNCLASSIFIED

Figure 3

NPG PHOTO NO. 2594 (APL)

Deep etched section of Italian 47mm H.E. projectile.

CEE No. 3662.

15 May 1945



UNCLASSIFIED



NPG Photo No. 2651 (APL)



Figure 4

UNCLASSIFIED


MICROSTRUCTURE OF THE BODY OF  
ITALIAN 47mm HE PROJECTILE

Fine Pearlite and Ferrite

Hardness - 92 Rb      Magnification 250X

Etch - Picral      M493

15 June 1945

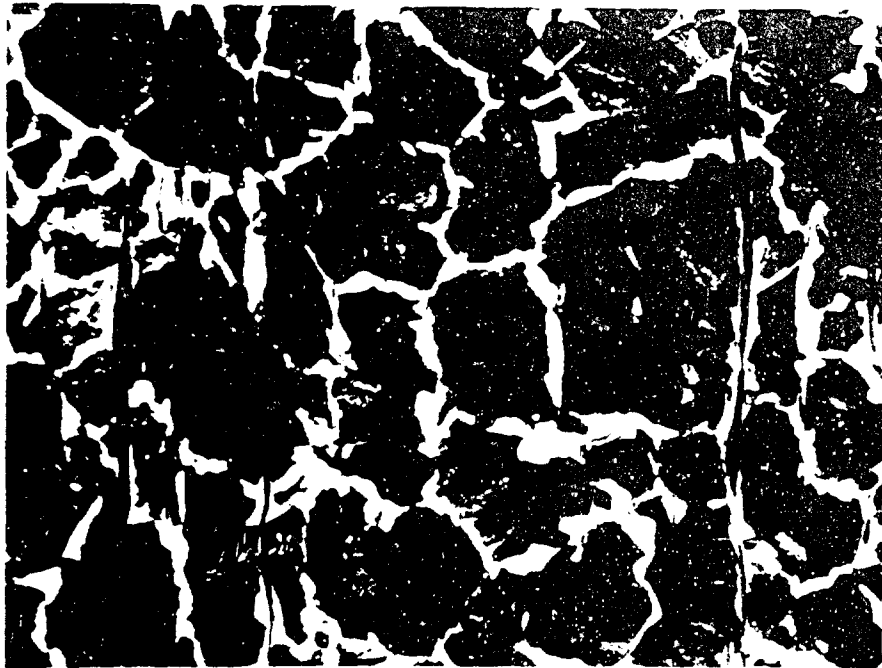

UNCLASSIFIED

## I: INTRODUCTION

One Italian 47mm H.E. round was received at the Naval Proving Ground for complete physical, chemical, and metallurgical examination. The following is a report of this investigation in accordance with the directives.

## II. EXAMINATION

### PHYSICAL

The complete round, as received and disassembled, is shown in Figure 1-. The projectile extends into the case nearly half its length, and is fitted with a narrow rotating band near its center. A contact type nose fuze is provided. The markings found on the round are shown in Figure 2 and indicate that the case was manufactured in 1941, but give no indication as to the date of manufacture of the projectile. The colors used to identify the projectile and its loading are also given in Figure 2.

### CHEMICAL

A chemical analysis of the projectile body and rotating band is given in the table below. Steel analyses are spectrochemical with the exception of carbon, phosphorus, and sulphur which have been obtained by standard wet chemical methods.

	<u>C</u>	<u>Mn</u>	<u>P</u>	<u>S</u>	<u>Si</u>	<u>Ni</u>	<u>Cr</u>	<u>Mo</u>	<u>Cu</u>	<u>Al</u>
Body	.56	.82	.022	.080	.18	<.08	NTr	NTr	.11	NTr
	<u>Cu</u>	<u>Zn</u>	<u>Sn</u>	<u>Fe</u>	<u>P</u>					
Band	99.87	None	None	.091	.043					
NTr =	No trace									

The projectile has been machined from a plain carbon steel with an analysis similar to SAE 1055. Attention is invited to the high sulphur content of this steel probably added for increased machinability. The rotating band is copper.

### METALLURGICAL

The projectile body was split longitudinally and deep etched to reveal the flow lines. Figure 3 shows the etched section and indicates that the projectile was machined from bar stock. A uniform hardness of approximately 92 Rb was obtained along the surface of the body. The microstructure of the projectile body is shown in Figure 4. It consists of fine pearlite and ferrite and has a relatively large number of non-metallic inclusions.

UNCLASSIFIED

UNCLASSIFIED

#### DISCUSSION

The subject projectile body was manufactured from a plain carbon steel. It was machined from bar stock and was given a single heat treatment probably consisting of an air cool from above the critical temperature.

UNCLASSIFIED

UNCLASSIFIED

III  
EXAMINATION OF ONE ITALIAN  
105mm H.E. PROJECTILE  
CEE NO. 3651

SUMMARY

This projectile was produced by piercing and forging. It was made from a high manganese, free machining steel similar to SAE x 1345. The chemical analysis of the projectile and its components are given.

UNCLASSIFIED

UNCLASSIFIED

CONTENTS

	<u>Page</u>
I. INTRODUCTION . . . . .	1
II. EXAMINATION - Physical, Chemical, Metallurgical . .	1
III. DISCUSSION . . . . .	2

LIST OF FIGURES


	<u>Opposite</u> <u>Page</u> -----
Fig. 1 NPG Photo No. 1404 (APL) As Received and Disassembled View . . . . .	1
Fig. 2 NPG Photo No. 2550 (APL) Markings on Projectile . . . . .	1
Fig. 3 NPG Photo No. 2555 (APL) Deep Etched Section	1
Fig. 4 NPG Photo No. 2652 (APL) Microstructures . .	2

UNCLASSIFIED




Figure 1

NPG Photo No. 1404 (APL)  
As received and disassembled view of Italian 105mm  
H. E. projectile. CEE No. 3651.  
15 May 1945



UNCLASSIFIED

UNCLASSIFIED

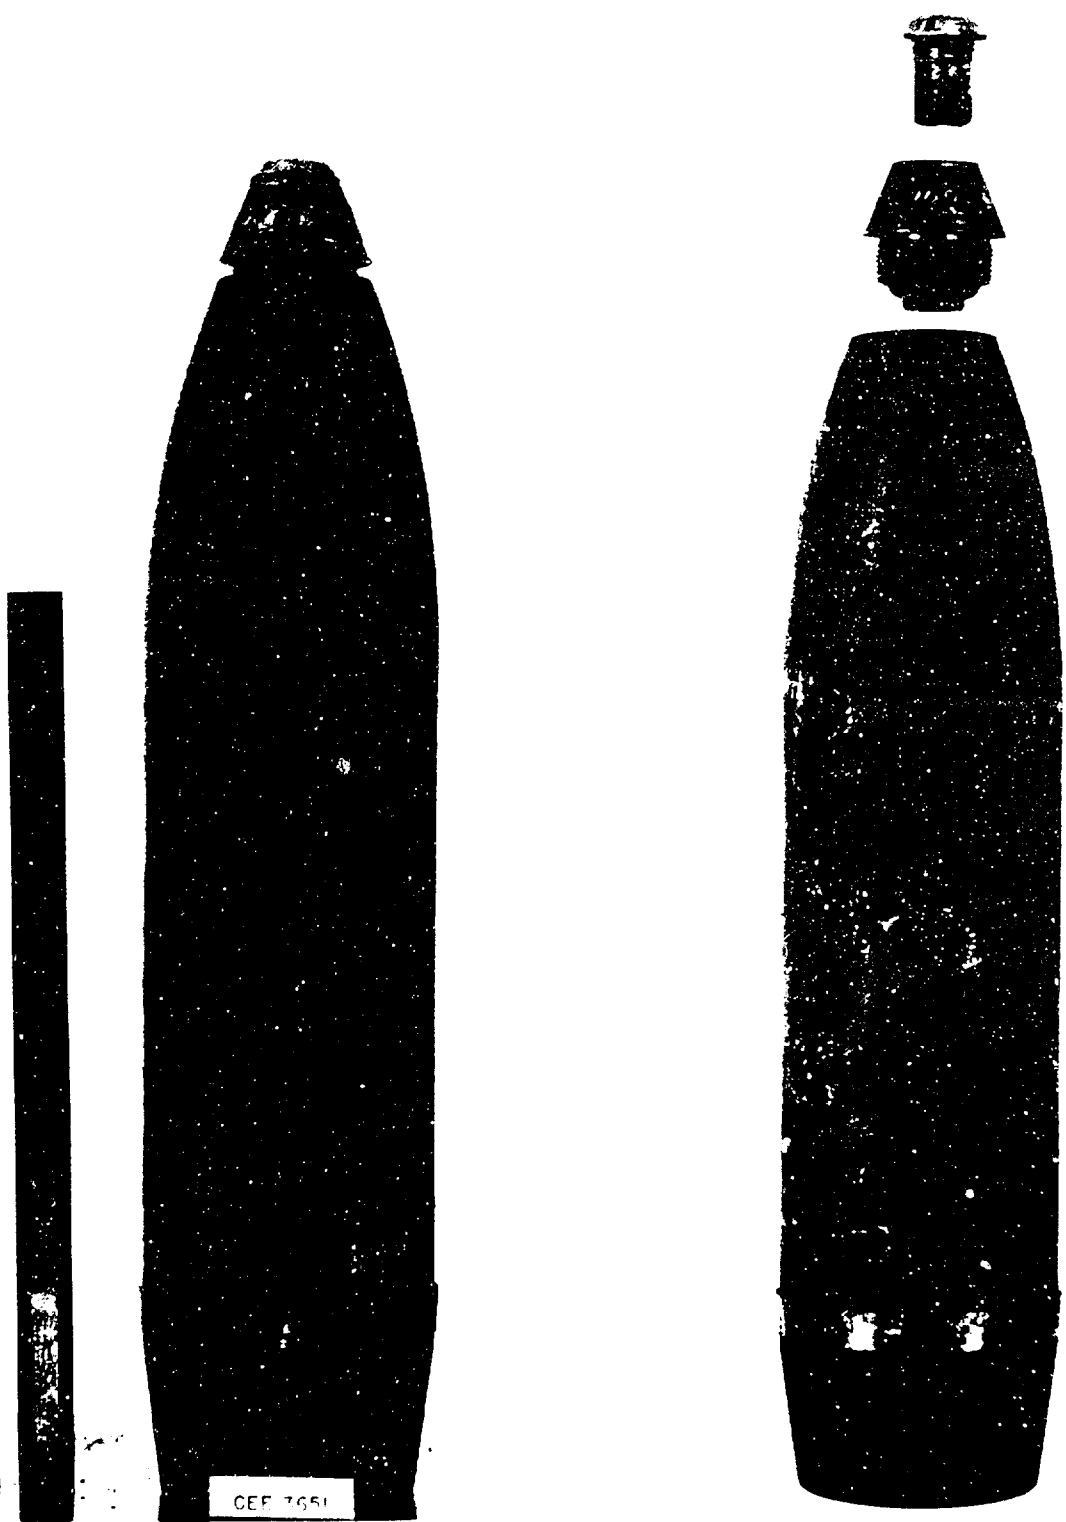


UNCLASSIFIED

CEE 3651

UNCLASSIFIED

MARKINGS ON ITALIAN  
105mm HE PROJECTILE

CEE 3651

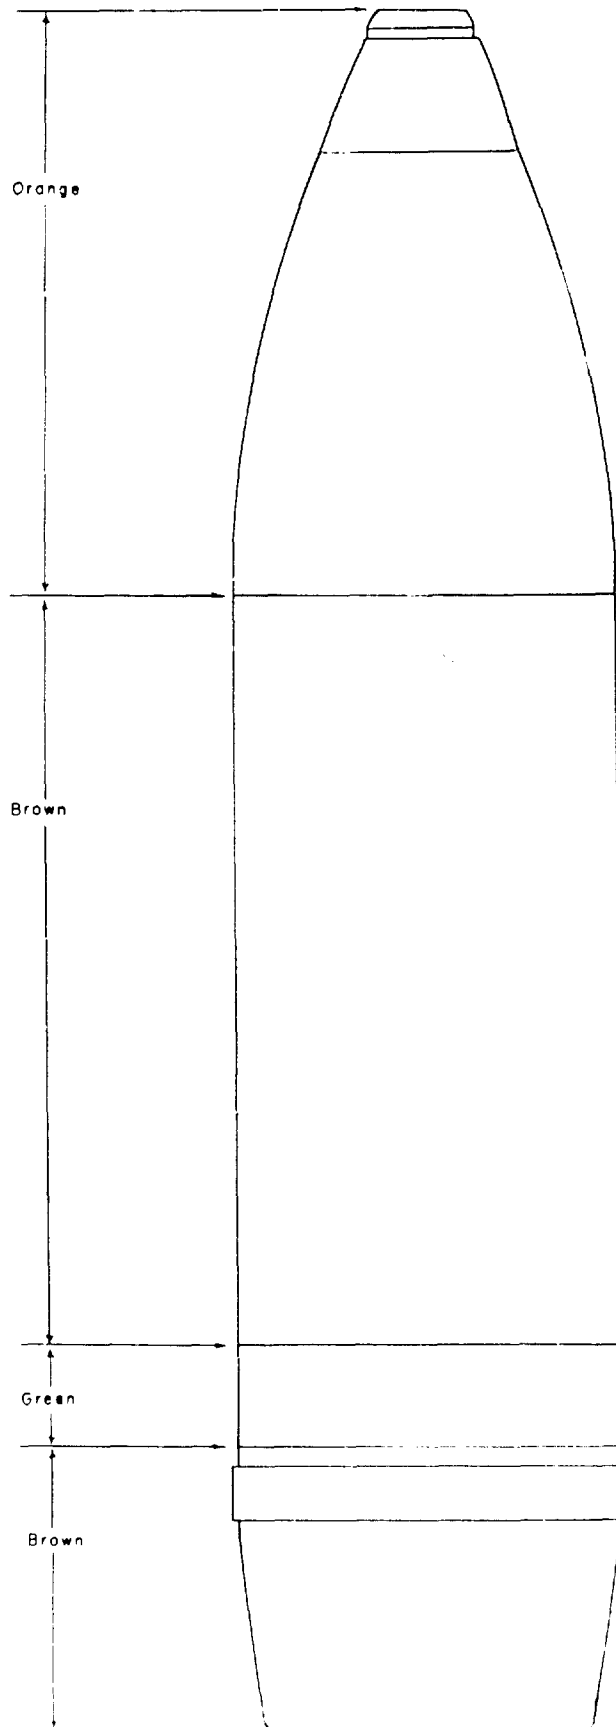

Indistinct Stenciling  
MIGL 98

Kg. 16.050  
AMATOLO 80/20  
R.B. - X  
105/78

Figure 3

NPG PHOTO NO. 2555 (APL)

Deep etched section of Italian 105mm H.E. projectile.

CEE No. 3651.

15 May 1945

NPG PHOTO NO. 2555 (APL)



## I. INTRODUCTION

One Italian 105mm H.E. projectile was received at the Naval Proving Ground for complete physical, chemical and metallurgical examination. The following is a report of this investigation in accordance with the directives.

## II. EXAMINATION

## PHYSICAL

Figure 1 shows the projectile as received and disassembled. A nose plug is provided with a threaded hole in the end for a detonating fuze. The projectile was received with a shipping plug screwed into the fuze hole.- The markings found on the projectile and its identifying coloring are shown in the drawing of Figure 2. There is no opening in the base of the projectile and only a very narrow rotating band is provided.

## CHEMICAL

A chemical analysis of the projectile body and its components is given in the table below. Steel analyses are spectrochemical excepting carbon, phosphorus and sulphur which have been obtained by standard wet chemical methods.

Nose	<u>C</u>	<u>Mn</u>	<u>P</u>	<u>S</u>	<u>Si</u>	<u>Ni</u>	<u>Cr</u>	<u>Mo</u>	<u>Cu</u>
Plug	.29	.90	.044	.074	.20	<.08	NTr	NTr	.18
Body	.48	1.25	.023	.049	.20	.16	<.08	.01	.14
	<u>Cu</u>	<u>Zn</u>	<u>Sn</u>	<u>Fe</u>	<u>P</u>				
Band	99.86	.024	.047	.049	.019				

NTr : No Trace

The nose plug was manufactured from a plain carbon steel corresponding to SAE 1030 while the body of the projectile was made from a free machining high manganese steel similar to SAE X 1345. The rotating band is copper.

## METALLURGICAL

The projectile body was sectioned longitudinally with an abrasive cut-off wheel and deep etched to reveal the flow lines. The deep etched section is shown in Figure 3. The distribution and direction of the flow lines indicate that the projectile was upset forged and pierced to

Figure 1

NPG PHOTO NO. 1852 (APL).





As received and disassembled view of Italian 120mm

Common projectile CEE No. 3437.

15 May 1945



~~UNCLASSIFIED~~

UNCLASSIFIED

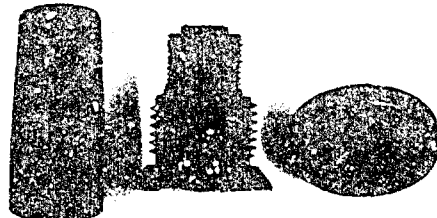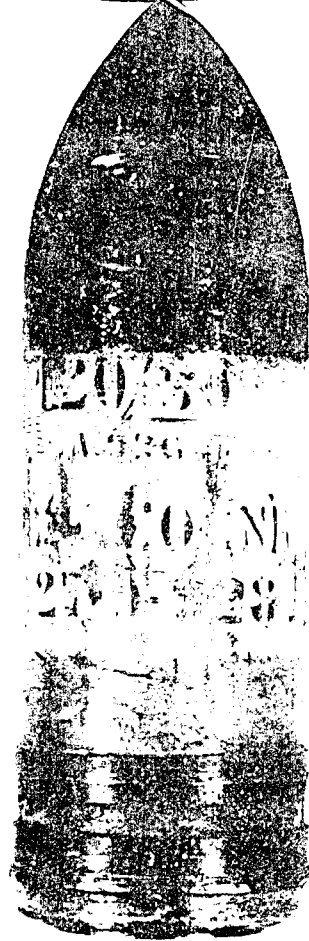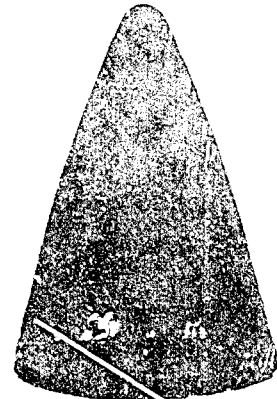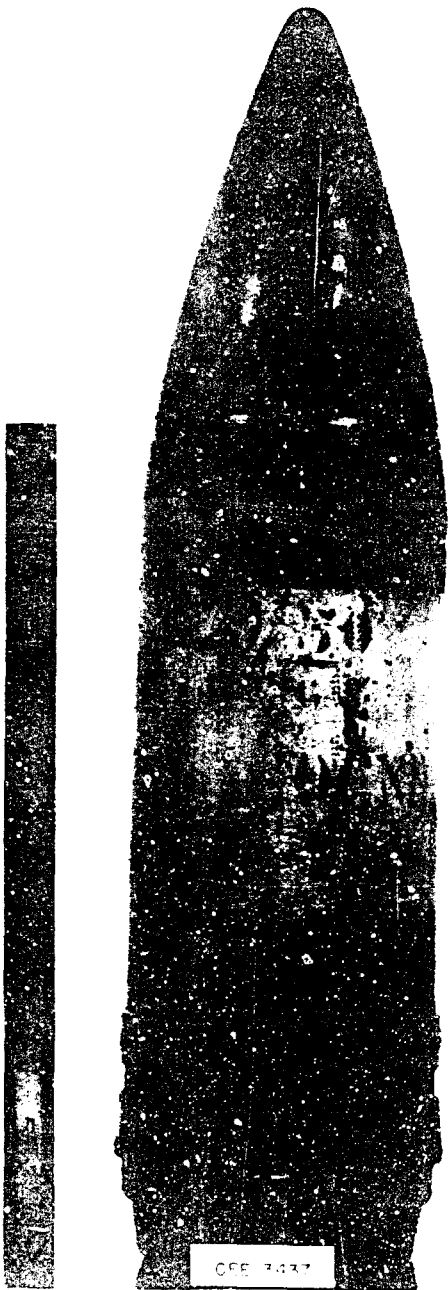

UNCLASSIFIED

MARKINGS ON ITALIAN  
20 mm COMMON PROJECTILE

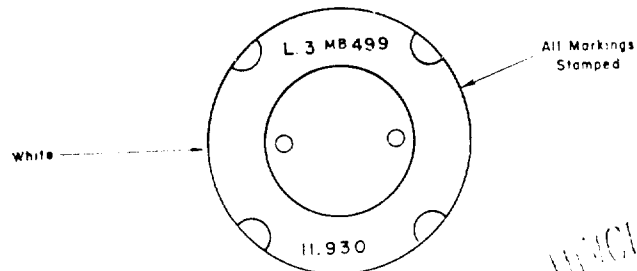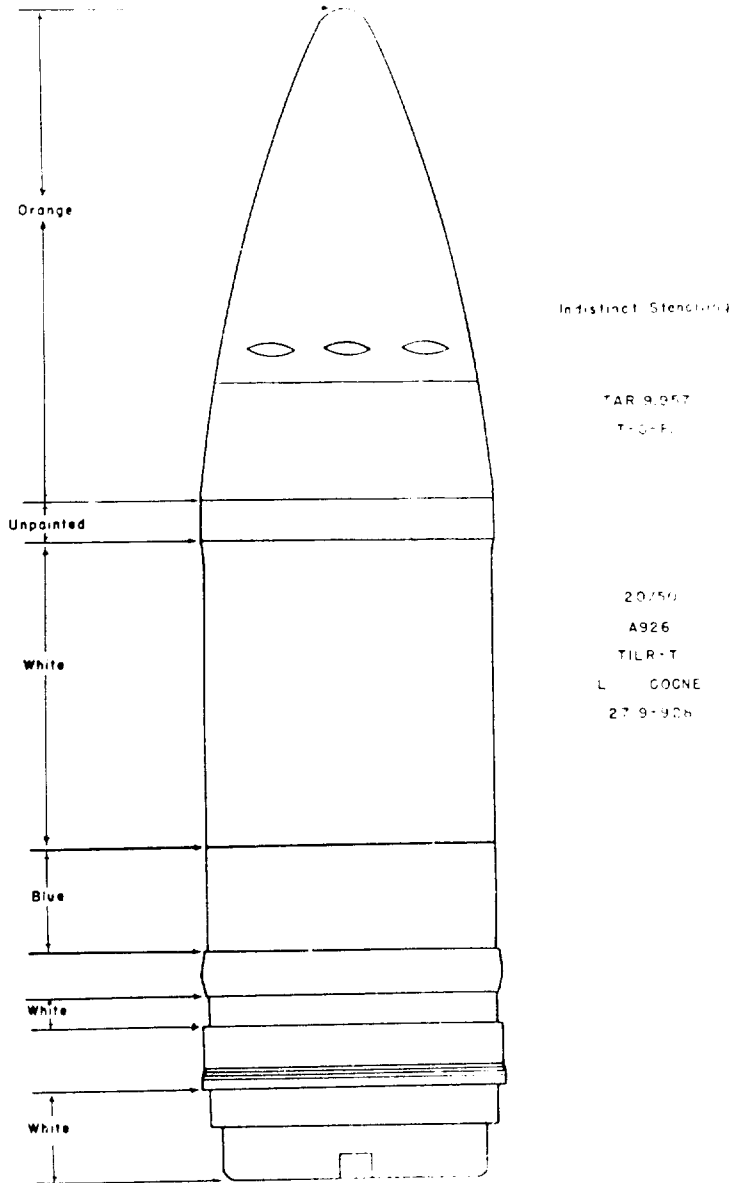


UNCLASSIFIED

UNCLASSIFIED

Figure 4  
HARDNESS DISTRIBUTION AND MACROSECTION  
OF ITALIAN 120mm COMMON PROJECTILE

Hardness Values: Mickers Pyramid (50 Kg)  
Etch: Ammonium Persulphate

GFE 3437

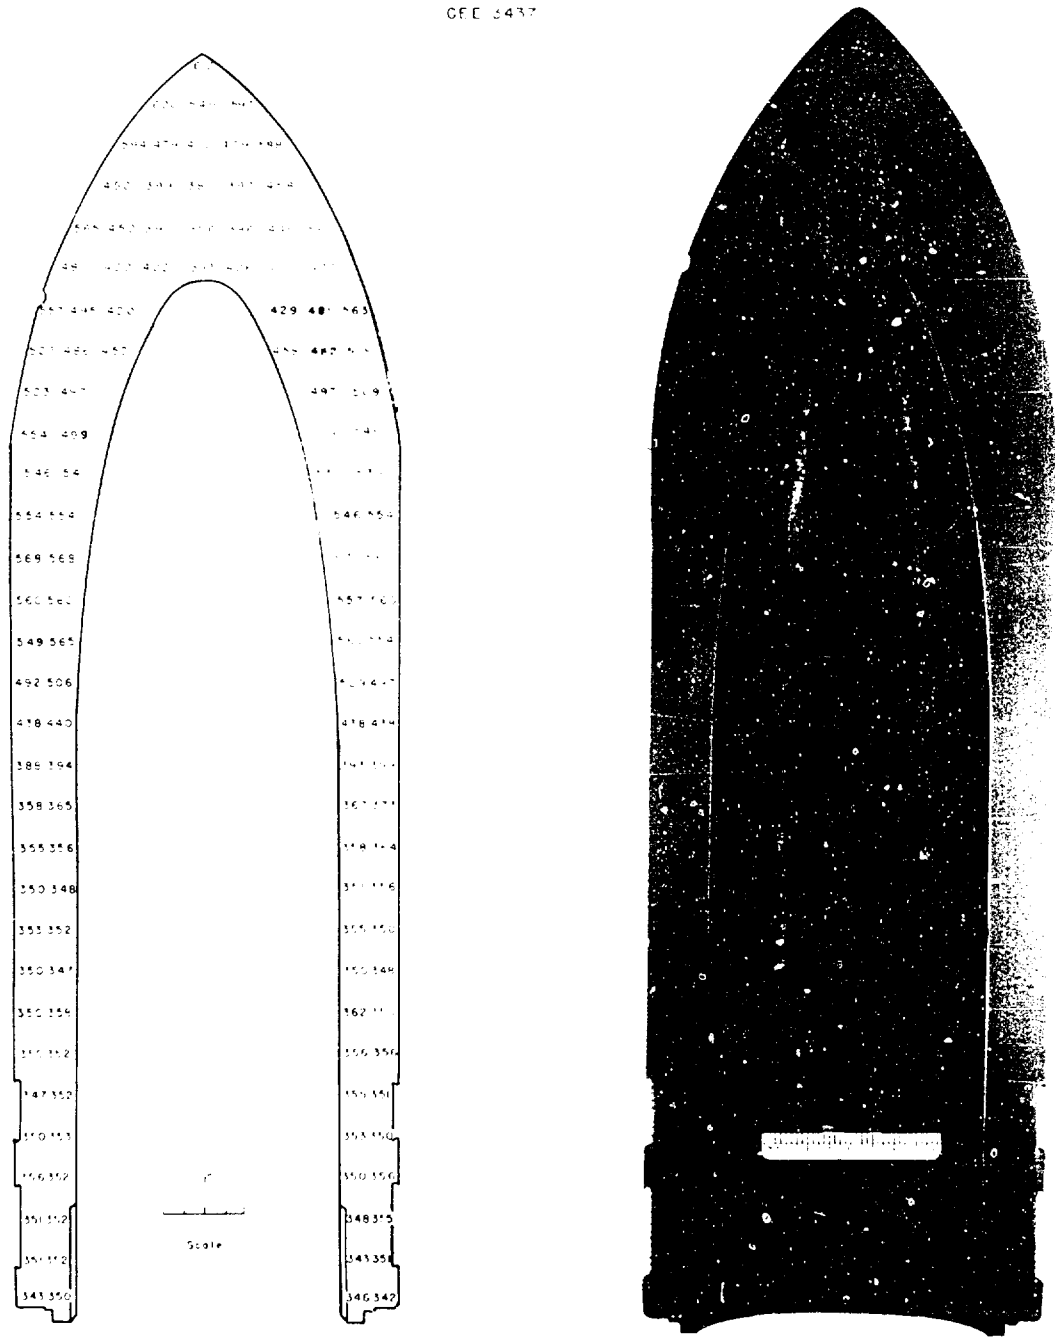


NPG Photo No. 2551 (APL)  
May 15, 1945

UNCLASSIFIED

UNCLASSIFIED


Figure 4

MICROSTRUCTURES OF  
ITALIAN 105mm HE PROJECTILE

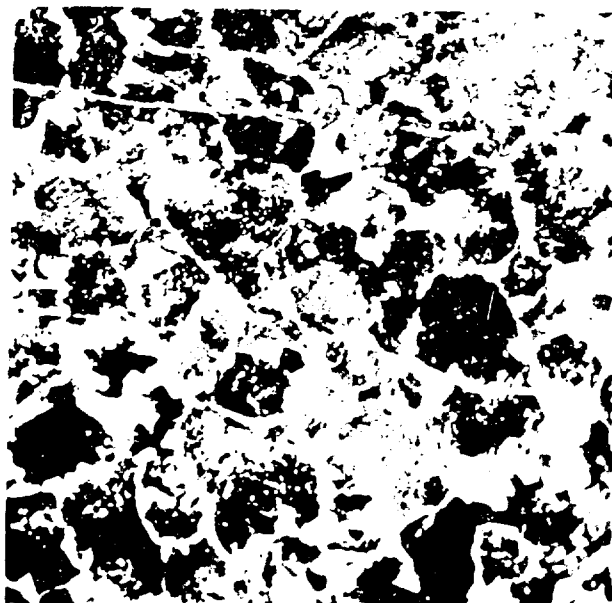

BODY Pearlite and  
Ferrite

Hardness - 99 Rb  
Magnification - 250X  
Etch - Picral  
M499

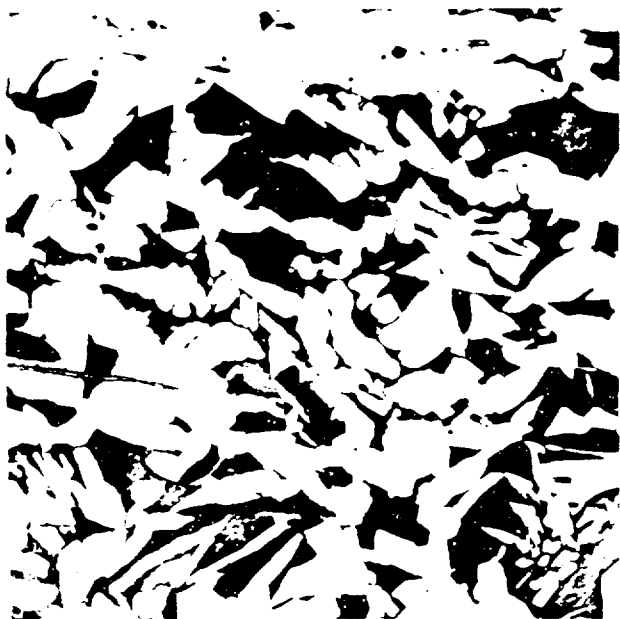

NOSE PLUG Pearlite and  
Ferrite

Hardness - 78 Rb  
Magnification - 250X  
Etch - Picral  
M498

NPG Photo No. 2652 (APL)  
15 June 1945

~~XXXXXXXXXX~~  
UNCLASSIFIED



UNCLASSIFIED

IV

EXAMINATION OF ONE ITALIAN

120mm COMMON PROJECTILE

CEE NO. 3437

SUMMARY

This projectile was manufactured from a 0.47% carbon nickel-chrome steel by a forging operation. It was uniformly hardened and then base drawn. The complete hardness pattern is given and the chemical composition of all its components was determined.

UNCLASSIFIED

## CONTENTS

	<u>Page</u>
I. INTRODUCTION . . . . .	1
II. EXAMINATION - Physical, Chemical, Metallurgical . .	1
III. DISCUSSION . . . . .	2

## LIST OF FIGURES

	<u>Opposite Page</u> -----
Fig. 1 NPG Photo No. 1852 (APL) As Received and Disassembled View . . . . .	1
Fig. 2 NPG Photo No. 2442 (APL) Markings on Projectile. . . . .	1
Fig. 3 NPG Photo No. 2551 (APL) Hardness Distribution. . . . .	1
Fig. 4 NPG Photo No. 2444 (APL) Base Plug . . . . .	2
Fig. 5 NPG Photo No. 2653 (APL) Microstructures . .	2
Fig. 6 NPG Photo No. 2654 (APL) Microstructures . .	2

UNCLASSIFIED

form the cavity. The nose was shaped by forging and then finish machined. A hardness of approximately 99 Rb was obtained on the surface of the projectile body. In Figure 4 is shown the microstructure of the nose plug and body, both consist of ferrite and pearlite, the amount of pearlite present being in proportion to the carbon content of the steel. The nose plug had a uniform hardness of 78 Rb.

### III DISCUSSION

A high manganese, free machining, steel has been used in the manufacture of this projectile. It has been manufactured by forging and piercing and has not received any special heat treatment. The microstructure indicates that it was normalized by heating to above the critical temperature and cooling in air. The microstructure, heat treatment and hardness are similar to U.S. Navy projectiles of this type and size.

UNCLASSIFIED

## I. INTRODUCTION

One Italian 120mm Common projectile was received at the Naval Proving Ground for complete physical, chemical and metallurgical examination. The following is a report of this investigation in accordance with the directives.

II. EXAMINATION  
PHYSICAL

Figure 1 shows the projectile as received and disassembled. It is provided with a windshield crimped to the ogive, a base plug and base detonating fuze. Two rotating bands are used. The markings found on the projectile and its identifying colors are given in Figure 2.

## CHEMICAL

A chemical analysis of the projectile body and its components is given in the table below. Steel analyses are spectrochemical excepting carbon, phosphorus and sulphur which have been obtained by standard wet chemical methods.

	<u>C</u>	<u>Mn</u>	<u>P</u>	<u>S</u>	<u>Si</u>	<u>Ni</u>	<u>Cr</u>	<u>Mo</u>	<u>Cu</u>
Windshield	.06	.38	.005	.032	NTr	<.08	NTr	NTr	.18
Body	.45	.51	.032	.014	.78	.55	.81	NTr	.18
Base Plug	.47	.54	.030	.024	.25	<.08	NTr	NTr	NTr
	<u>Cu</u>	<u>Zn</u>	<u>Fe</u>	<u>P</u>					
Bands	99.80	.011	.082	.106					

NTr = No Trace

The windshield of this projectile has been manufactured from a low carbon rimmed steel similar to that used for thin sheet to be processed by deep drawing. The projectile body is made from a fairly high carbon nickel-chrome steel and the base plug is plain carbon steel similar to SAE 1050. The rotating bands are copper.

## METALLURGICAL

The projectile body was sectioned longitudinally with an abrasive cut-off wheel and its hardness distribution determined over the entire cross section. Figure 3 shows the results of the hardness survey together with the etched section of the split projectile. A maximum hardness of approximately 600 VHN (55Rc) has been obtained on




Figure 4

NFG PHOTO NO. 2444 (AFL).

Bottom view and deep etched section of base plug of  
Italian 120mm Common projectile CEE No. 3437.

15 May 1945

UNCLASSIFIED

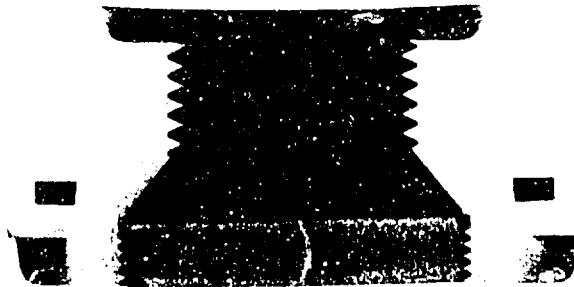

UNCLASSIFIED

UNCLASSIFIED


Figure 5

MICROSTRUCTURES OF  
ITALIAN 120mm COMMON  
PROJECTILES



PROJECTILE NOSE Martensite  
with Bainite Needles

Hardness - 600 VPN  
Magnification - 1000X  
Etch - Picral Nital  
M495

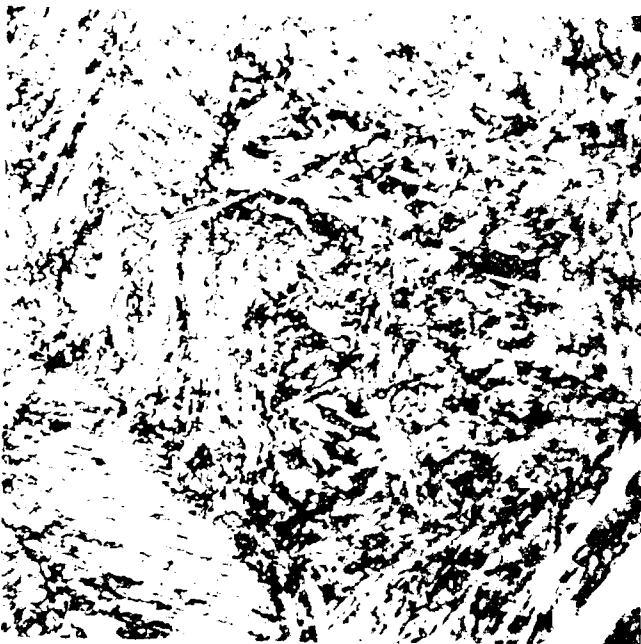

PROJECTILE BASE Tempered  
Martensite


Hardness - 350 VPN  
Magnification - 1000X  
Etch - Picral  
M496

NPG Photo No. 2653 (APL)  
25 June 1945

UNCLASSIFIED

Figure 6

MICROSTRUCTURES OF  
ITALIAN 120mm COMMON  
PROJECTILE

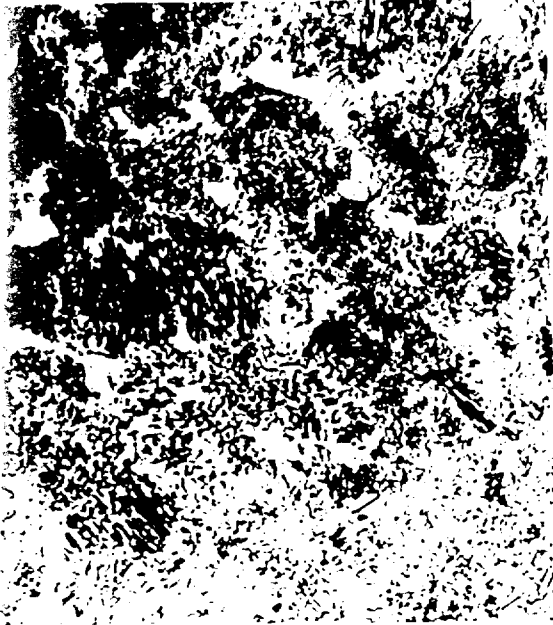

BASE PLUG Spherodized  
Pearlite

Hardness - 92 Rb  
Magnification - 500X  
Etch - Picral  
M497



WINDSHIELD Ferrite and  
Traces of Pearlite

Hardness - 68 Rb  
Magnification - 250X  
Etch - Nital  
M494

NPG Photo No. 2654 (APL)  
15 June 1945

UNCLASSIFIED

UNCLASSIFIED

the nose of the projectile. The hardness drops off uniformly from the nose to the middle of the body at which point it levels off at about 350 VPN (36Rc). Flow lines in the etch section indicate that the projectile was produced by a forging operation. In Figure 4 is shown a bottom view and deep etched section of the base plug, which also has been produced by forging. The cap seen covering the fuze hole has been machined from bar stock as indicated by the straight flow lines running through it. The base plug had a uniform hardness of 92 Rb.

Photomicrographs of the projectile body are given in Figure 5. Both the nose and base are quenched and tempered structures consisting of carbides and tempered martensite. The microstructure of the base plug and wind-shield are shown in Figure 6. The base plug has a structure consisting of spheroidized pearlite and the windshield is largely ferrite with traces of pearlite.

### III DISCUSSION

This projectile has been forged from a fairly high carbon nickel-chrome steel. A maximum hardness of approximately 600 VPN (55Rc) has been obtained on the nose and the base has a uniform hardness of approximately 350 VPN (36Rc). It is interesting to note that the nose hardness is practically the same as that of the U.S. Navy 5" common projectile Mk. 46 but the base is somewhat harder. The Mk. 46 has a base hardness of between 280 and 300 VPN (27.5 to 30Rc).

From the photomicrographs and etch section it appears that this projectile has been heat treated to a uniform hardness of 600 VPN and then base drawn. It is probable that it would have fairly good plate penetrative qualities for the size of cavity used.

UNCLASSIFIED



UNCLASSIFIED

V

EXAMINATION OF ONE ITALIAN 149mm H.E. PROJECTILE  
CEE NO. 3648

SUMMARY

Metallurgical data and chemical analyses of the principal components of this projectile are presented together with the probable method of manufacture of the body and nose piece.

The nature of the cavity indicates that this projectile is a chemical type.

UNCLASSIFIED

UNCLASSIFIED

CONTENTS

		<u>Page</u>
I.	INTRODUCTION . . . . .	1
II.	EXAMINATION - Physical, Metallurgical, Chemical. .	1
III.	DISCUSSION . . . . .	2

LIST OF FIGURES

		<u>Opposite</u> <u>Page</u>
Fig. 1	NPG Photo No. 2793 (APL) . . . . . As Received and Disassembled	1
Fig. 2	NPG Photo No. 2549 (APL) Drawing . . . . .	1
Fig. 3	NPG Photo No. 2596 (APL) Macro Etch Section. .	1
Fig. 4	NPG Photo No. 2666 (APL) Photomicrographs. . .	2

UNCLASSIFIED

Figure 1

NPG Photo No. 2793 (APL).  
As received and disassembled view of Italian 149mm  
H.E. projectile, CEE No. 3648.  
15 May 1945





FIGURE 2  
MARKINGS ON ITALIAN  
149 mm HE PROJECTILE

CEE 3648

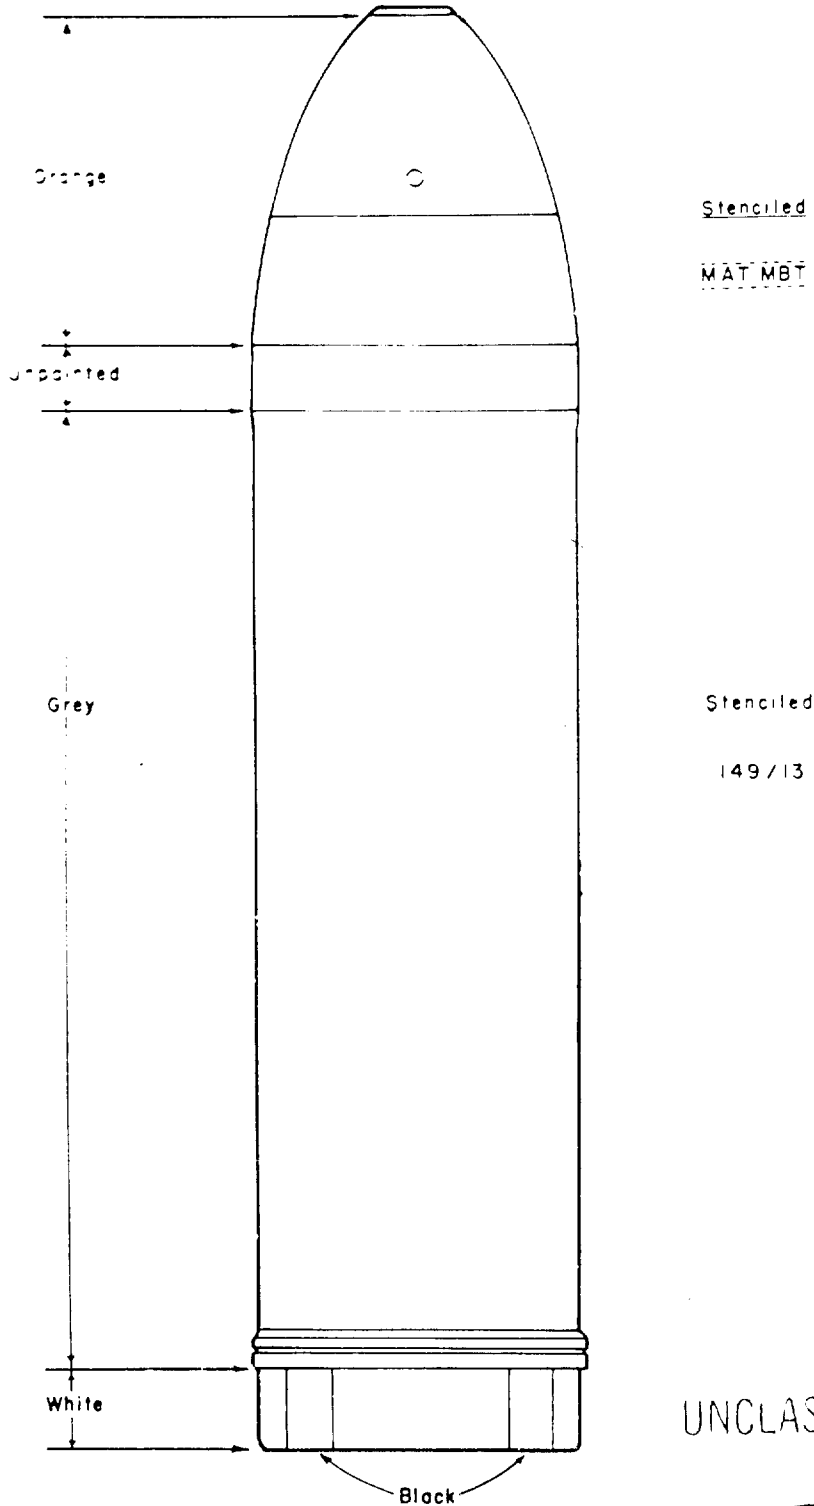

NPG Photo No. 2549 (APL)  
May 15, 1945

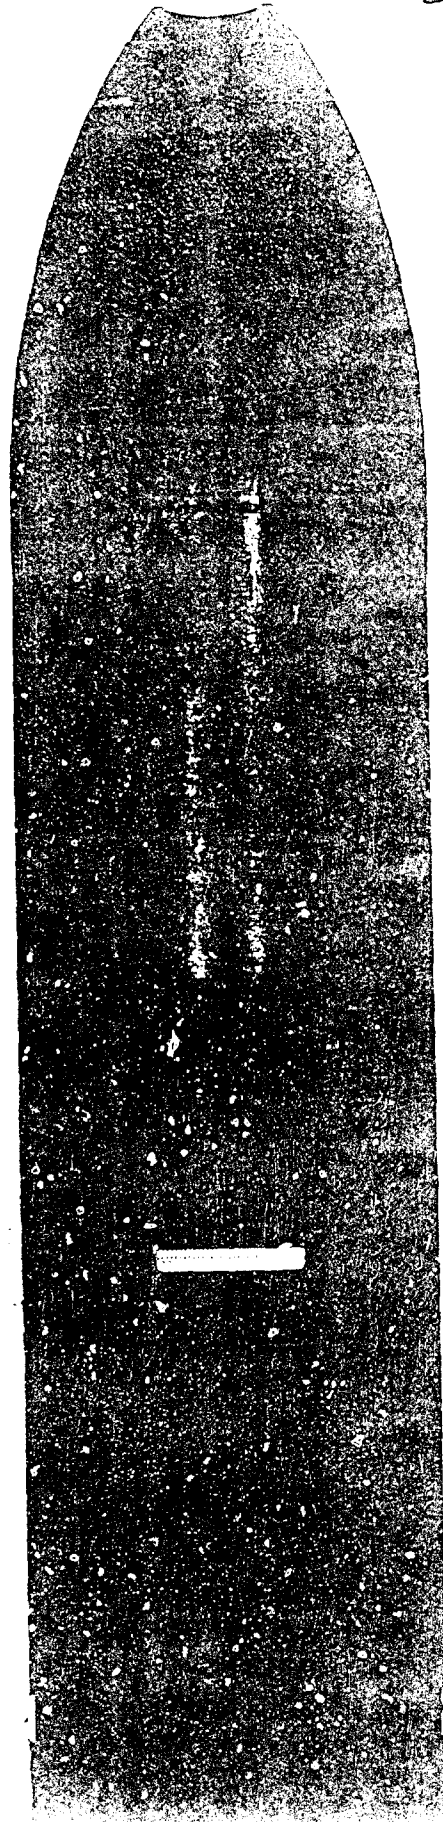


Figure 3

NPG Photo No. 2596 (APL).  
Deep etched section of Italian 149mm H.E. projectile.  
CEE No. 3648.  
15 May 1945



UNCLASSIFIED



UNCLASSIFIED

UNCLASSIFIED

I. INTRODUCTION

One Italian high explosive 149mm projectile was examined in accordance with the directive. A report of the examination follows.

II. EXAMINATION

PHYSICAL

Figure 1 shows the projectile as received and disassembled. The projectile body has a large cavity which is divided about midway by a transverse threaded steel disk having 4 vent holes. This construction suggests that the projectile carried a dual loading, the forward charge as a burster and the rear charge as a smoke, incendiary, or gas filling. The body is threaded at the forward end to take a large nose piece which is itself threaded to provide for a nose fuze.

A single narrow rotating band was attached in the usual way. Figure 2 shows the details of painting and marking.

CHEMICAL ANALYSIS

The chemical analyses of the important components are given below. Steel analyses are spectrochemical, except for the elements carbon phosphorus, and sulfur which were obtained by the usual wet chemical methods.

	<u>C</u>	<u>Mn</u>	<u>P</u>	<u>S</u>	<u>Si</u>	<u>Ni</u>	<u>Cr</u>	<u>Mo</u>	<u>Cu</u>
Body	.73	.94	.034	.074	.08	.13	<.08	NTr	.18
Nose	.48	.59	.088	.053	.17	NTr	NTr	NTr	.08
	<u>Cu</u>	<u>Sn</u>	<u>Zn</u>	<u>Fe</u>					
Band	99.91	.030	.032	.017					

The body is made of a steel similar to SAE 1075 with high sulfur content, and the nose is made of a steel similar to SAE 1045 with high phosphorus content. The copper of the rotating band is of high purity.

The etch pattern of the nose section and of the body are shown in Figure 3. Flow lines indicate that the body was pierced and the nose section forged.

Both body and the nose section were uniform in hardness.

Nose Hardness 94 Rockwell "B"


Body Hardness 98 Rockwell "B"

UNCLASSIFIED

UNCLASSIFIED

Figure 4

MICROSTRUCTURES OF  
ITALIAN 149mm HE PROJECTILE

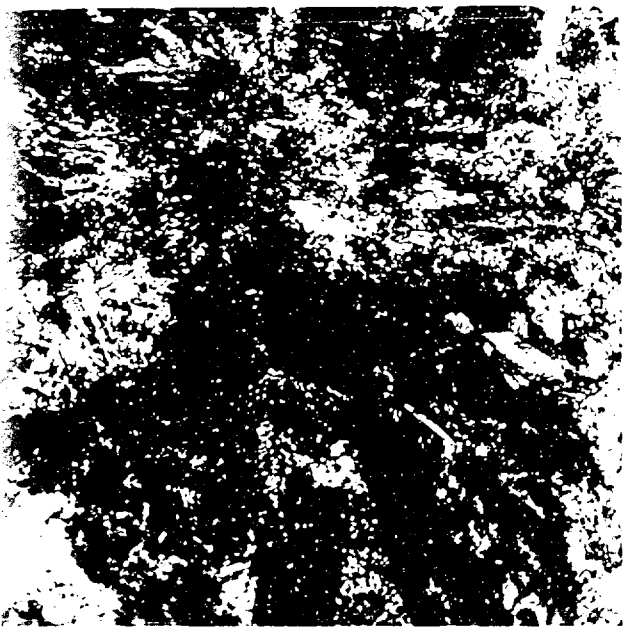

BODY      Pearlite

Hardness - 98 Rb  
Magnification - 250X  
Etch - Picral  
M500



NOSE SECTION      Pearlite  
and Ferrite

Hardness - 94 Rb  
Magnification - 250X  
Etch - Picral  
M501

NPG Photo No. 2666 (APL)  
15 June 1945

UNCLASSIFIED

## UNCLASSIFIED

The microstructure of the nose and body are shown in Figure 4. Both nose and body are normalized structures, the microstructure of the body consisting of pearlite, and that of the nose consisting of pearlite and ferrite.

The probable steps in the manufacture of this projectile are given below:

- |      |                |
|------|----------------|
| Body | a. Piercing    |
|      | b. Normalizing |
|      | c. Machining   |
| Nose | a. Forging     |
|      | b. Normalizing |
|      | c. Machining   |

### III. DISCUSSION

, This projectile was probably satisfactory for its intended purpose. The prime consideration in its heat treatment was machinability. The exact nature of the loading is unknown, but it was probably of the chemical type, smoke, incendiary or gas.

UNCLASSIFIED



UNCLASSIFIED

VI

EXAMINATION OF ONE ITALIAN 6" H.E. PROJECTILE

CEE NO. 3435

SUMMARY

Metallurgical data and chemical analyses of the principal components of this projectile are presented together with the probable methods of manufacture of the body and base plug.

The projectile body and base plug are made of plain carbon steel.

UNCLASSIFIED

UNCLASSIFIED

CONTENTS

	<u>Page</u>
I. INTRODUCTION . . . . .	1
II. EXAMINATION- Physical, Chemical, Metallurgical . . .	1
III. DISCUSSION . . . . .	2

LIST OF FIGURES

	<u>Opposite</u> <u>--Page--</u>
Fig. 1 NPG Photo No. 1385 (APL) As Received and Disassembled View . . .	1
Fig. 2 NPG Photo No. 2556 (APL) Drawing . . . .	1
Fig. 3 NPG Photo No. 2558 (APL) Base Plug . . .	2
Fig. 4 NPG Photo No. 2561 (APL) Deep Etched Section of Body . . . . .	2
Fig. 5 NPG Photo No. 2564 (APL) Microstructure	2

Table A: Chemical Analyses

UNCLASSIFIED

Table A UNCLASSIFIED

CHEMICAL ANALYSES OF ITALIAN 6<sup>mm</sup> H.E. COMPONENTS

	<u>C</u>	<u>P</u>	<u>S</u>	<u>Si</u>	<u>Mn</u>	<u>Ni</u>	<u>Cr</u>	<u>Cu</u>
Projectile Body:	.35	.013	.033	.21	.69	--	<.08	.20
Base Plug:	.54	.032	.051	.12	.57	<.08	--	.19

	<u>Si</u>	<u>Fe</u>	<u>Cu</u>	<u>Mn</u>	<u>Zn</u>	<u>Ti</u>	<u>Trace</u>	<u>Balance</u>
Windshield:	12.19	1.31	.19	.075	.075	.29	Mg,Pb	Al.

	<u>Cu</u>	<u>P</u>	<u>Fe</u>	<u>Zn</u>
Rotating Band:	99.81	.124	.041	.025


  

	<u>Pb</u>	<u>Sn</u>	<u>Trace</u>
Sealing Ring:	99.92	.052	Sb,Bi,Ag.

UNCLASSIFIED

Italian 6" HE Projectile, CEE No. 3435, as received and description view.  
15 May 1945

UNCLASSIFIED


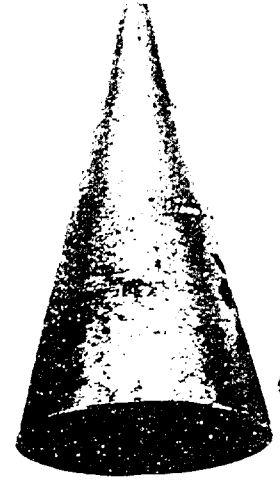


UNCLASSIFIED



MARKINGS ON ITALIAN  
6" HE PROJECTILE

GEE 5415

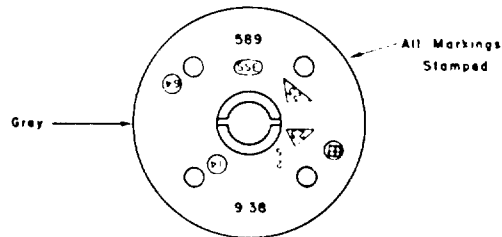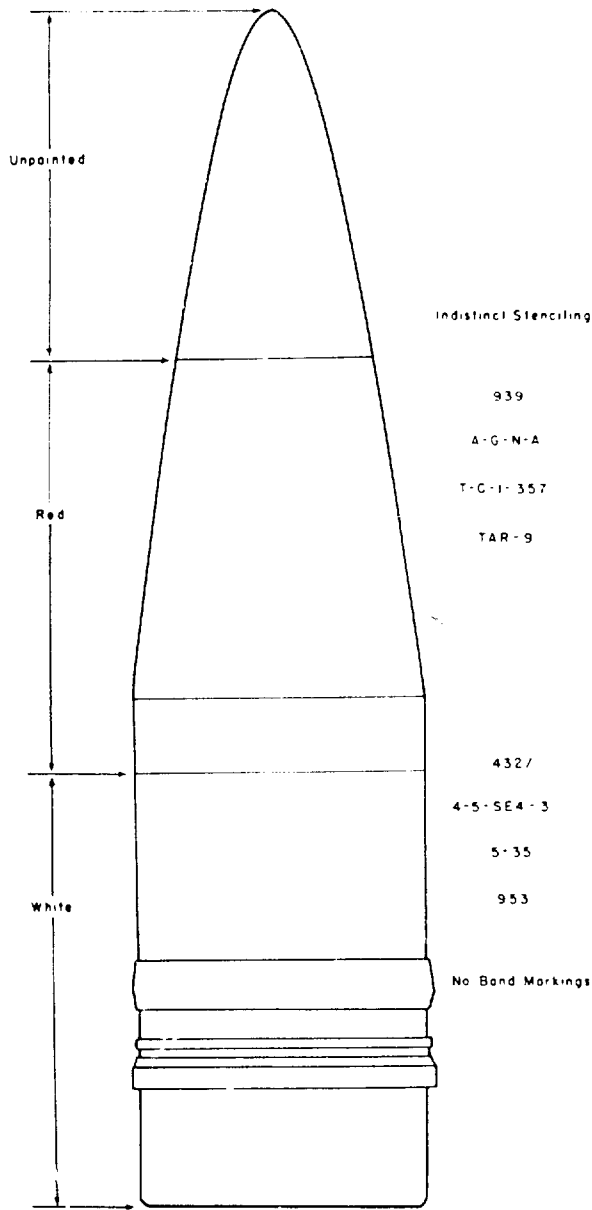

NPG Photo No 2556 (APL)  
May 15, 1945

UNCLASSIFIED

## I. INTRODUCTION

One Italian high explosive 6" projectile was examined. The following is a report of this examination, in accordance with the directive.

II. EXAMINATION  
PHYSICAL

Figure 1 shows the projectile as received and disassembled. The projectile body is threaded at the nose internally to receive the point detonating fuze and externally to receive the cast aluminum windshield. A massive base plug is secured in the base of the projectile by means of "V" threads. This base plug carries an internal tracer. Immediately behind the point detonating fuze, which is of the impact type, is a flash tube also threaded to the projectile body. The flash tube, made of plastic with cloth filler, leads to the booster enclosed in a brass can which apparently was inserted into a cavity in the explosive filler.

The projectile was provided with two rotating bands located respectively 2-1/8" and 3-7/8" from the base. These bands were securely attached to the body in the conventional manner.

An unusual feature is the fact that the fuze is covered by the windshield. The fuze is made of brass, and was made bore safe by a clock escapement calculated to delay the arming. It appeared to be of the nondelay type.

The details of painting and marking are shown in Figure 2. For the most part stenciling was indistinct.

## CHEMICAL ANALYSIS

The chemical analyses of the important components are given in Table A. Steel analyses are spectrochemical except for carbon, phosphorus, and sulfur which were obtained by the usual wet chemical methods.


The projectile body and base plug analyses are similar to those of SAE-1035 and SAE-X 1050 respectively.

The aluminum windshield has a composition approximating that of Alcoa Alloy 47, a sand casting alloy. The 12.5% Si alloy is used extensively in Europe.

The rotating bands on this projectile are made of copper which is impure compared to that used in American practice.

NPG PHOTO NO. 2558 (APL) Figure 3  
Bottom View and Deep Etched Section of Base Plug From  
Italian 6" HE Projectile CEE No. 3435.  
15 May 1945


UNCLASSIFIED

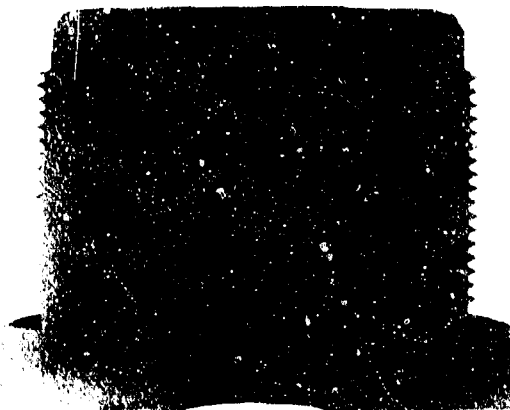

UNCLASSIFIED

Figure 4  
NPG PHOTO NO. 2561 (APL)  
Deep Etched Section of Body of Italian 6" HE Projectile  
CEE No. 3435.  
15 May 1945

~~SECRET~~  
UNCLASSIFIED

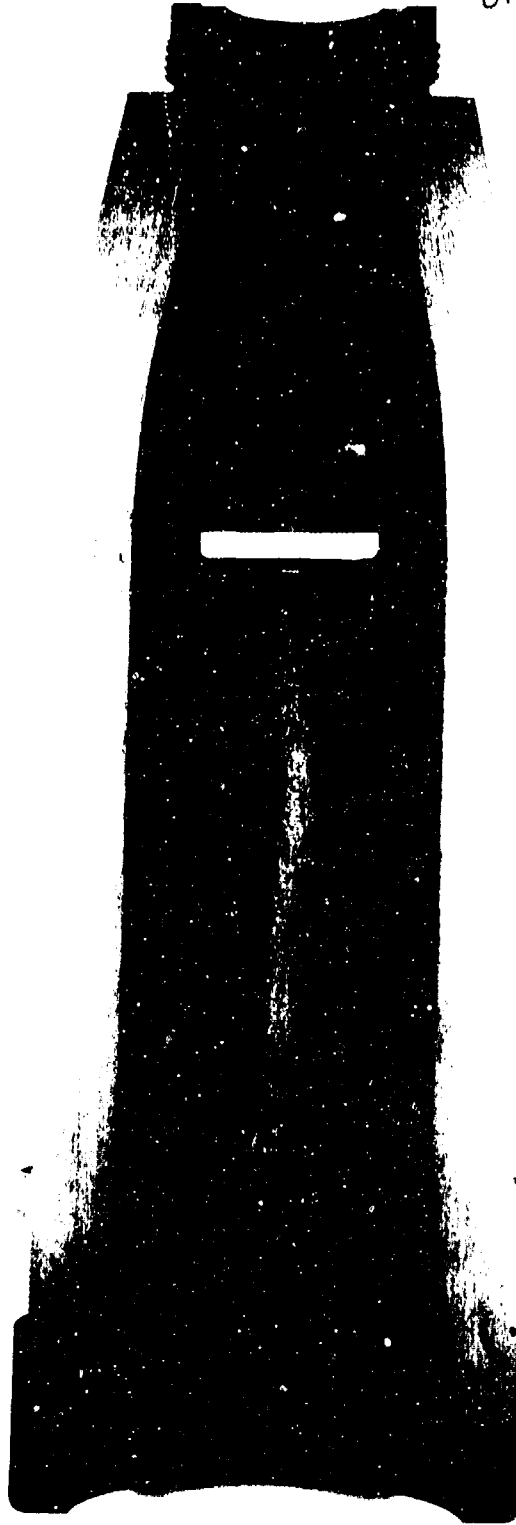




UNCLASSIFIED


Figure 5

MICROSTRUCTURES OF ITALIAN  
6" HE PROJECTILE

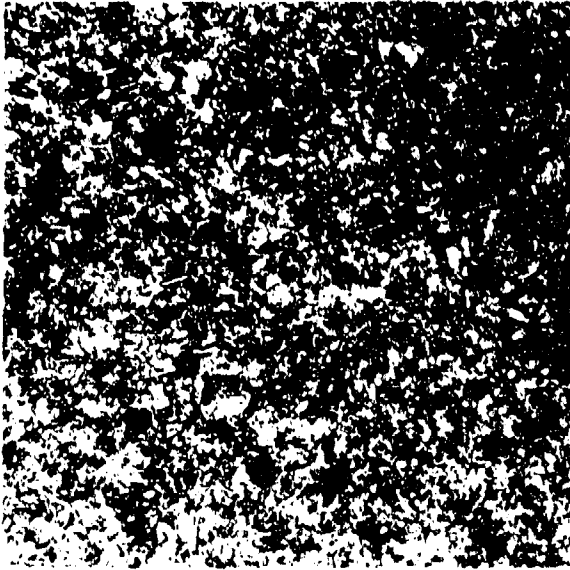

BODY Pearlite and Ferrite

Hardness: 260 VPN  
Magnification: 250 X  
Etch: Picral  
M522

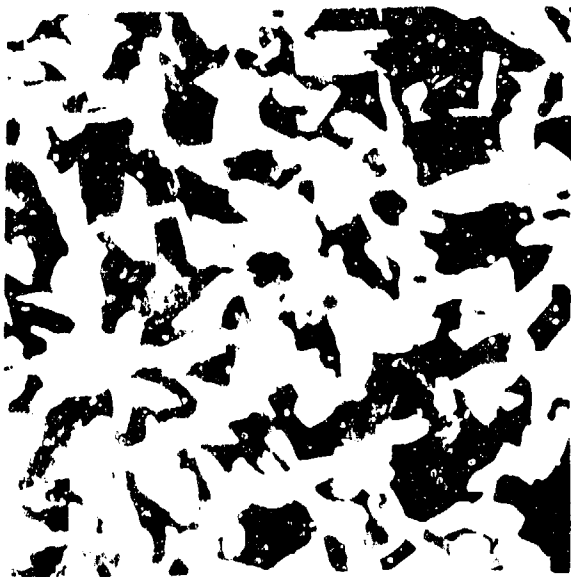

BASE PLUG Pearlite and Ferrite

Hardness: R<sub>p</sub>77  
Magnification: 250 X  
Etch: Picral  
M523

NPG Photo No. 2564 (AFL)  
15 June 1945

UNCLASSIFIED

METALLURGICAL UNCLASSIFIED

The deep etch pattern of the base plug and body are shown in Figures 3 and 4 respectively. The etch pattern of the projectile body shows flow lines indicating that this piece was forged. A small amount of upsetting is noted at the mouth of the cavity. The etch pattern of the base plug indicates that this piece was machined from bar stock.

The projectile body was sectioned and a hardness survey made. Its hardness was found to be uniform from nose to base. The hardnesses of the principal components are given below:

Body:	260 VPN
Base Plug:	77 Rb
Rotating Bands:	48-1/2 Rb

Figure 5 illustrates the microstructure of the body and base plug. Both structures consist of pearlite and ferrite. The fineness of the pearlite and the small amount of pro-eutectoid ferrite in the microstructure of the body suggest that this piece was quenched and tempered. This treatment did not result in high hardness since this steel has low hardenability. The microstructure of the base plug is a typical normalized structure.

The probable steps in the manufacture of this projectile are given below as far as is possible, consistent with the above information:

Body:	a Forging
	b Quench. This may have been from the finish forging temperature or a separate operation.
	c Low temperature draw (stress relief)
	d Machining
Base:	Machined directly from normalized bar stock.

### III DISCUSSION

This projectile is probably effectively used against any target offering little resistance to penetration. The presence of an instantaneous point detonating fuze precludes the use of this projectile for penetrating armor, concrete, or earthworks. The microstructure of the body and base plug is not satisfactory for the effective penetration of armor plate.

UNCLASSIFIED

Section VI, Page 2

UNCLASSIFIED

VII  
EXAMINATION AND BALLISTIC TEST OF ITALIAN 6"  
COMMON PROJECTILE CEE NO. 3438

SUMMARY

Metallurgical data and chemical analysis of the principal components of this projectile are presented together with the probable method of manufacture of the body and base plug.

Results of ballistic tests are presented which show this projectile to be of very poor ballistic quality.

UNCLASSIFIED

UNCLASSIFIED

CONTENTS

	<u>Page</u>
I. INTRODUCTION . . . . .	1
II. EXAMINATION- Physical, Chemical, Metallurgical . . . . .	1
III. BALLISTIC TEST . . . . .	2
IV. DISCUSSION . . . . .	3

LIST OF FIGURES


	<u>Opposite</u> <u>Page</u> -----
Fig. 1 NPG Photo No. 1403 (APL) As Received and Disassembled View . . . . .	1
Fig. 2 NPG Photo No. 2560 (APL) Drawing . . . . .	1
Fig. 3 NPG Photo No. 2557 (APL) Base Plug . . . . .	1
Fig. 4 NPG Photo No. 2562 (APL) Deep Etched Section of Body . . . . .	1
Fig. 5 NPG Photo No. 2563 (APL) Microstructure . . . . .	2
Fig. 6 NPG Photo No. 2691 (APL) Ballistic Test vs 2:4 STS Plate . . . . .	3
Fig. 7 NPG Photo No. 2692 (APL) Ballistic Test vs 0:98 STS Plate . . . . .	3

Table A: Chemical Analyses

UNCLASSIFIED

Figure 1  
NPG PHOTO NO. 1403 (APL)  
Italian 6" Common Projectile, CEE No. 3438, as Received  
and Disassembled View.  
15 May 1945

~~SECRET~~  
UNCLASSIFIED


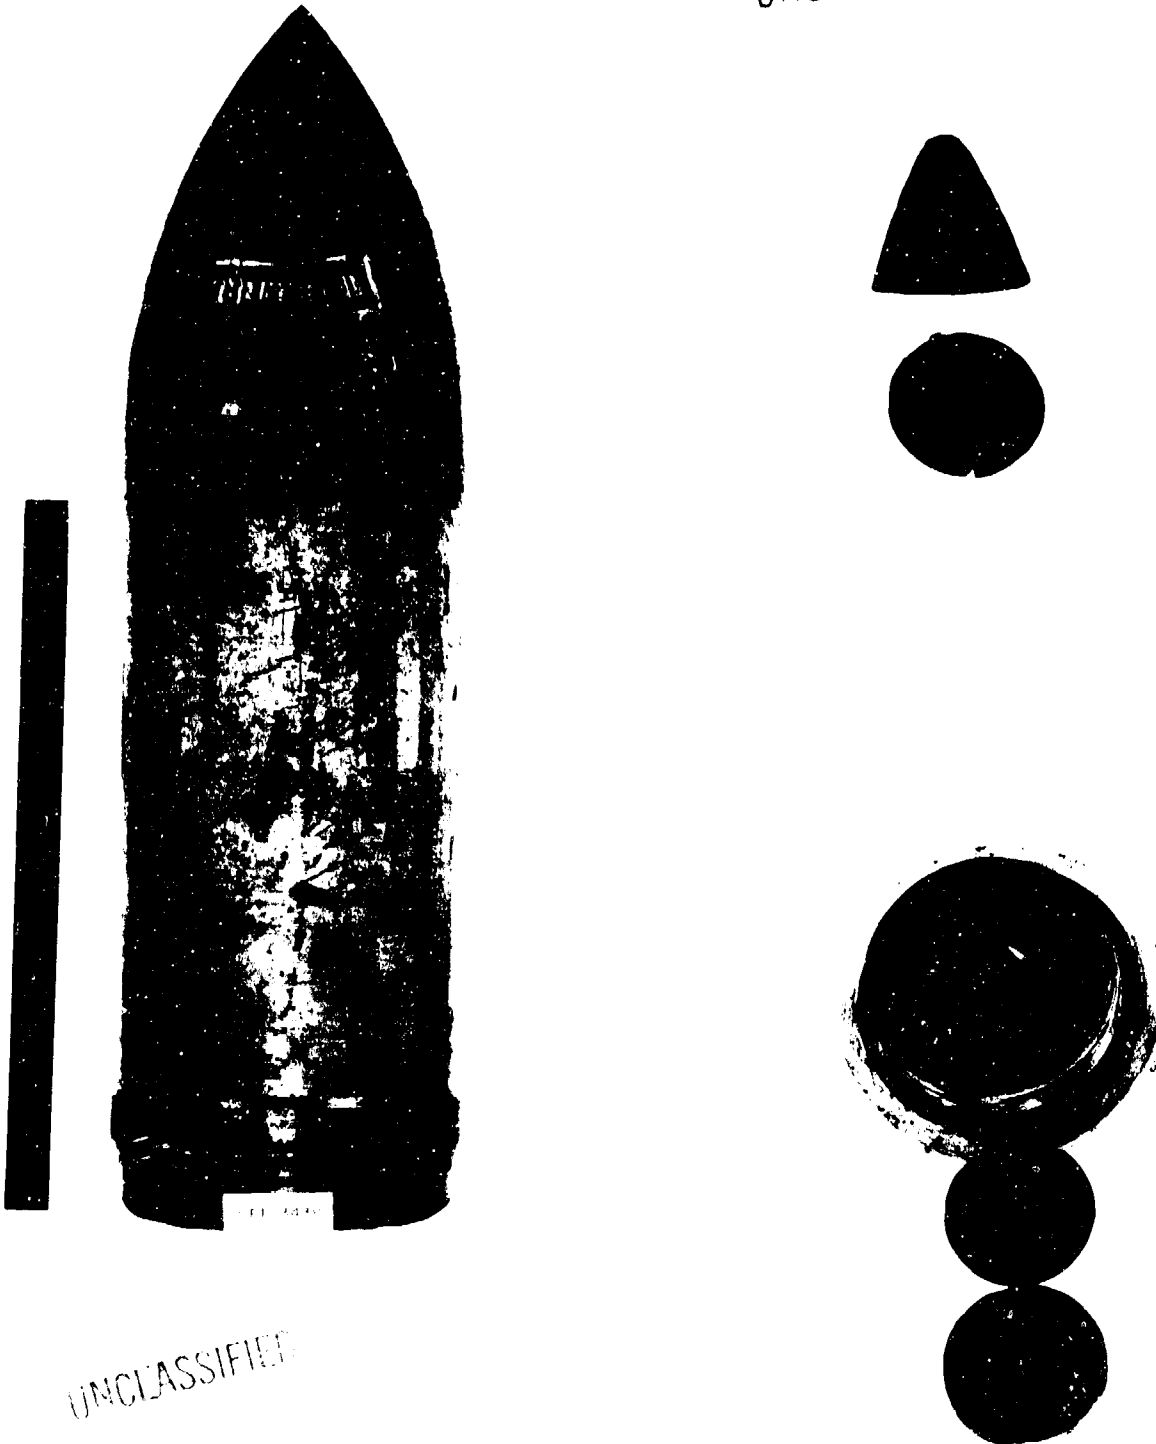


UNCLASSIFIED

UNCLASSIFIED

Figure 2  
MARKINGS ON ITALIAN  
6" COMMON PROJECTILE

CEE 3438

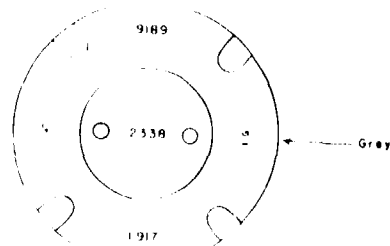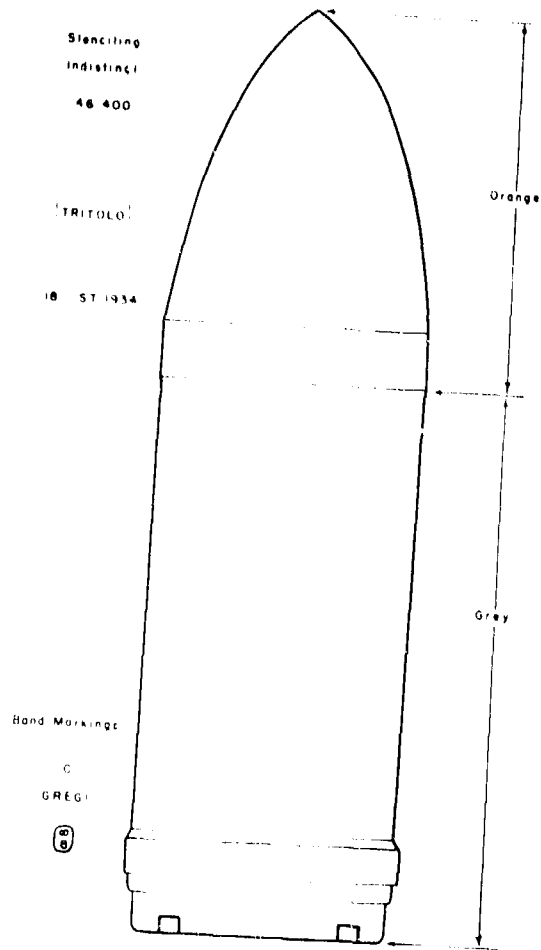


Markings on Body of Projectile are Stenciled  
Band and Base Markings are Stamped

NPG Photo No 2560 (APL)  
May 15, 1945

Figure 3  
NPG PHOTO NO. 2557 (APL)  
Bottom View and Deep Etched Section of Base Plug from  
Italian 6" Common Projectile, CEE No. 3438.  
15 May 1945

UNCLASSIFIED

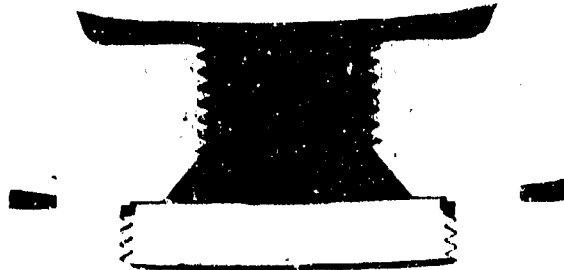


UNCLASSIFIED



NPG PHOTO NO. 2562 (APL) Figure 4  
Deep Etched Section of Body of Italian 6" Common Pro-  
jectile, CEE No. 3438.  
15 May 1945

~~SECRET~~  
UNCLASSIFIED

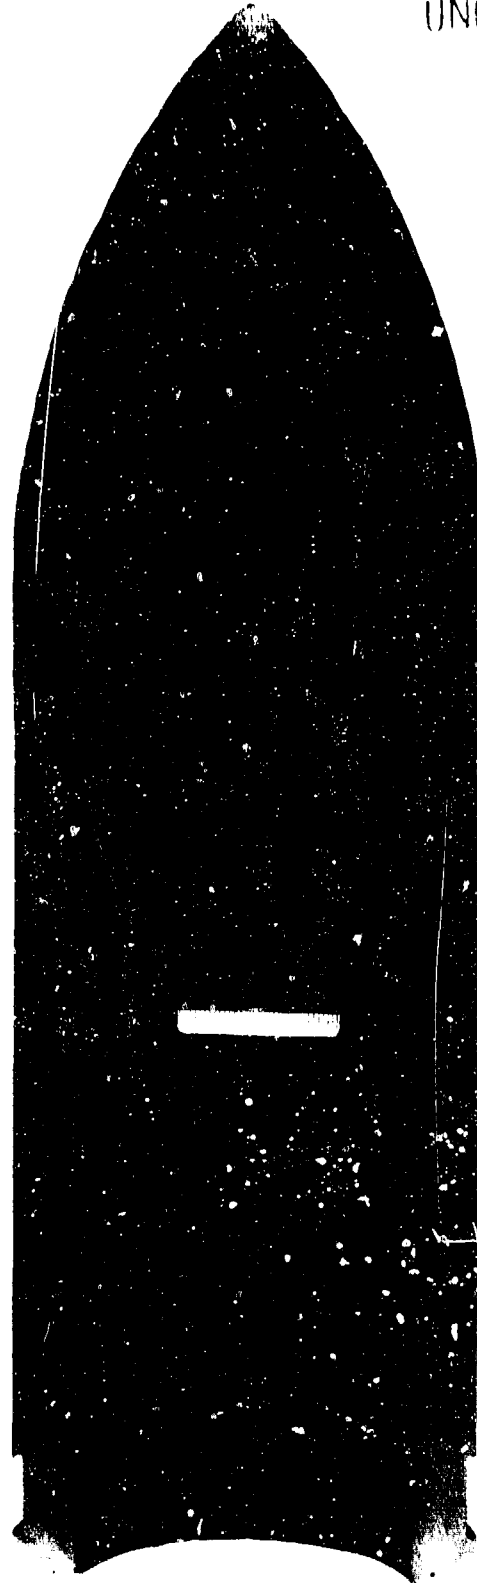

UNCLASSIFIED



Table A

UNCLASSIFIED

## CHEMICAL ANALYSES OF ITALIAN 6" COMMON PROJECTILE COMPONENTS

	<u>C</u>	<u>P</u>	<u>S</u>	<u>Si</u>	<u>Mn</u>	<u>N</u>	<u>Cr</u>	<u>Cu</u>
Body	.33	.034	.046	.21	.89	<.08	<.08	.12
Base Plug	.55	.032	.051	.26	.92	<.08	<.08	.09
	<u>Cu</u>	<u>Sn</u>	<u>Fe</u>					
Rotating Band	99.97	.023	.007					
Sealing Ring	99.95	.03	.02					
	<u>Pb</u>	<u>Sn</u>	<u>Trace</u>					
Lead Sealing Ring	99.90	.068	Cd, Ag					
Lead Sealing Disk	99.96	.034	Sb, Bi, Ag					

UNCLASSIFIED

## I. INTRODUCTION

UNCLASSIFIED

One Italian 6" Common projectile was examined and two of the same type were tested ballistically. The following is a report of the examination and of the ballistic tests in accordance with the directives. Although the directive lists this projectile as an AP, upon examination it was evident that it was a common projectile and this designation is therefore used.

## II. EXAMINATION PHYSICAL

This projectile is shown as received and disassembled in Figure 1. The projectile has no hood or windshield. The base plug is unique in that its outer edge forms the contour of the base end of the projectile. The base plug is threaded to take a base detonating fuze which in turn is protected from the propellant gases by a small disk screwed into the base plug behind the fuze. A wooden plug shaped to fit the forward end of the cavity and a felt-like pad are provided to act as a cushion for the explosive filler.

A single rotating band 1-1/4" from the base was securely attached by the conventional means.

All stenciled and stamped markings are indicated in Figure 2 which also indicates the painting. The stenciling was indistinct.

## CHEMICAL

The chemical analyses of the important metallic components are given in Table A. The analyses for steels were determined spectro-chemically except for the elements carbon, phosphorus, and sulfur, which were determined by the usual wet chemical methods.

The projectile body and base plug analyses are similar to those of SAE 1035 and SAE X 1055 analyses respectively. The copper in the rotating bands is of a purity comparable to that of American rotating bands. The sealing ring is also made of high purity copper.


The etch patterns of the base plug and of the body are shown in Figure 3 and 4 respectively. Both of these pieces show flow lines resulting from forging.

UNCLASSIFIED

UNCLASSIFIED


Figure 5

MICROSTRUCTURES OF ITALIAN  
6" COMMON PROJECTILE

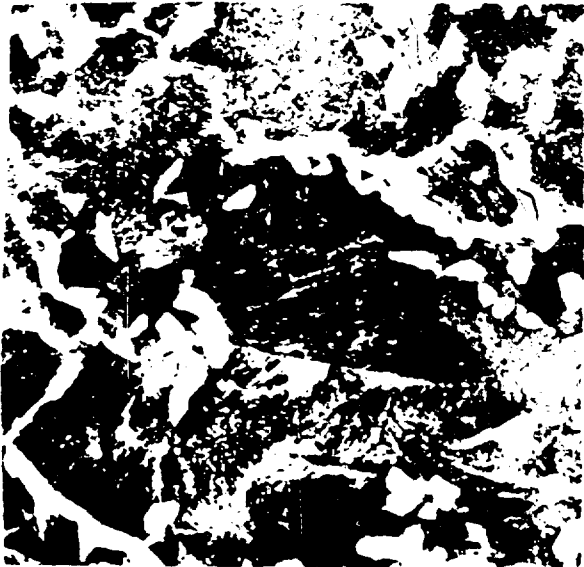

BODY Pearlite and Ferrite

Hardness: 200 VFN  
Magnification: 250 X  
Etch: Picral  
M520

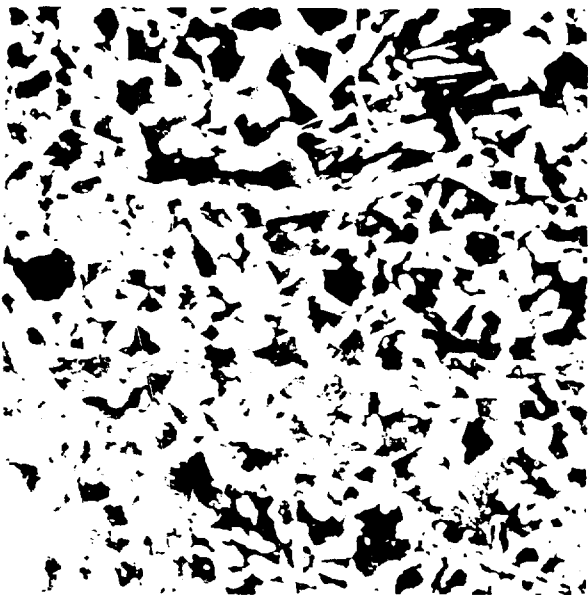

BASE PLUG Pearlite and Ferrite

Hardness: R<sub>B</sub> 85  
Magnification: 250 X  
Etch: Picral  
M521

NPG Photo 2563 (APL)  
15 June 1945  
~~XXXXXXXXXXXX~~

UNCLASSIFIED

## UNCLASSIFIED

The projectile body was sectioned and a hardness survey made. The hardness was found to be uniform. The hardnesses of the principle components are given below:

Body:	200 VFN
Base Plug:	R <sub>B</sub> 85
Rotating Band:	R <sub>B</sub> 27

Figure 5 shows the microstructure of the body and base plug. The body consists of coarse pearlite and of ferrite which is decidedly an undesirable structure ballistically. The base plug consists of pearlite and ferrite finer than that of the body. These are normalized structures.

The probable steps in the manufacture of this projectile are given below insofar as is consistent with the above information.

### Body and Base Plug.

- a. Forging
- b. Normalizing
- c. Machining

### III. BALLISTIC TESTS

Two rounds were tested ballistically. The first round was fired against 2-1/2" STS plate at 30° obliquity at a velocity about 10% above the limit velocity of average STS plate vs 6" common projectile Mk.27-7. This round was rejected by the plate completely broken up. Since nothing of value could be learned from further firing under these conditions, the second round was tested against 1" STS plate at 30° obliquity at a velocity greatly in excess of the plate limit. This round penetrated the plate and was effective with the tip of the nose chewed and the ogive gouged. The Mk. 27-7 projectile will remain effective and intact after penetrating considerably more than 2-1/2" STS at 30° obliquity. The test conditions of round 1 are less severe than the acceptance test conditions of the Mk. 27-7 projectile.

UNCLASSIFIED

NFC PHOTO NO. 2691 (APL). Ballistic Test of Italian 6" Common Projectile

Impact No. 30720  
Plate Thickness 2.40

Oblliquity 31°-20'

Striking Velocity 1052 ft/sec.

% of SK788A1 112.5


Penetration 1/2"

Remarks  
Projectile completely broken up.

3 March 1945

UNCLASSIFIED

UNCLASSIFIED

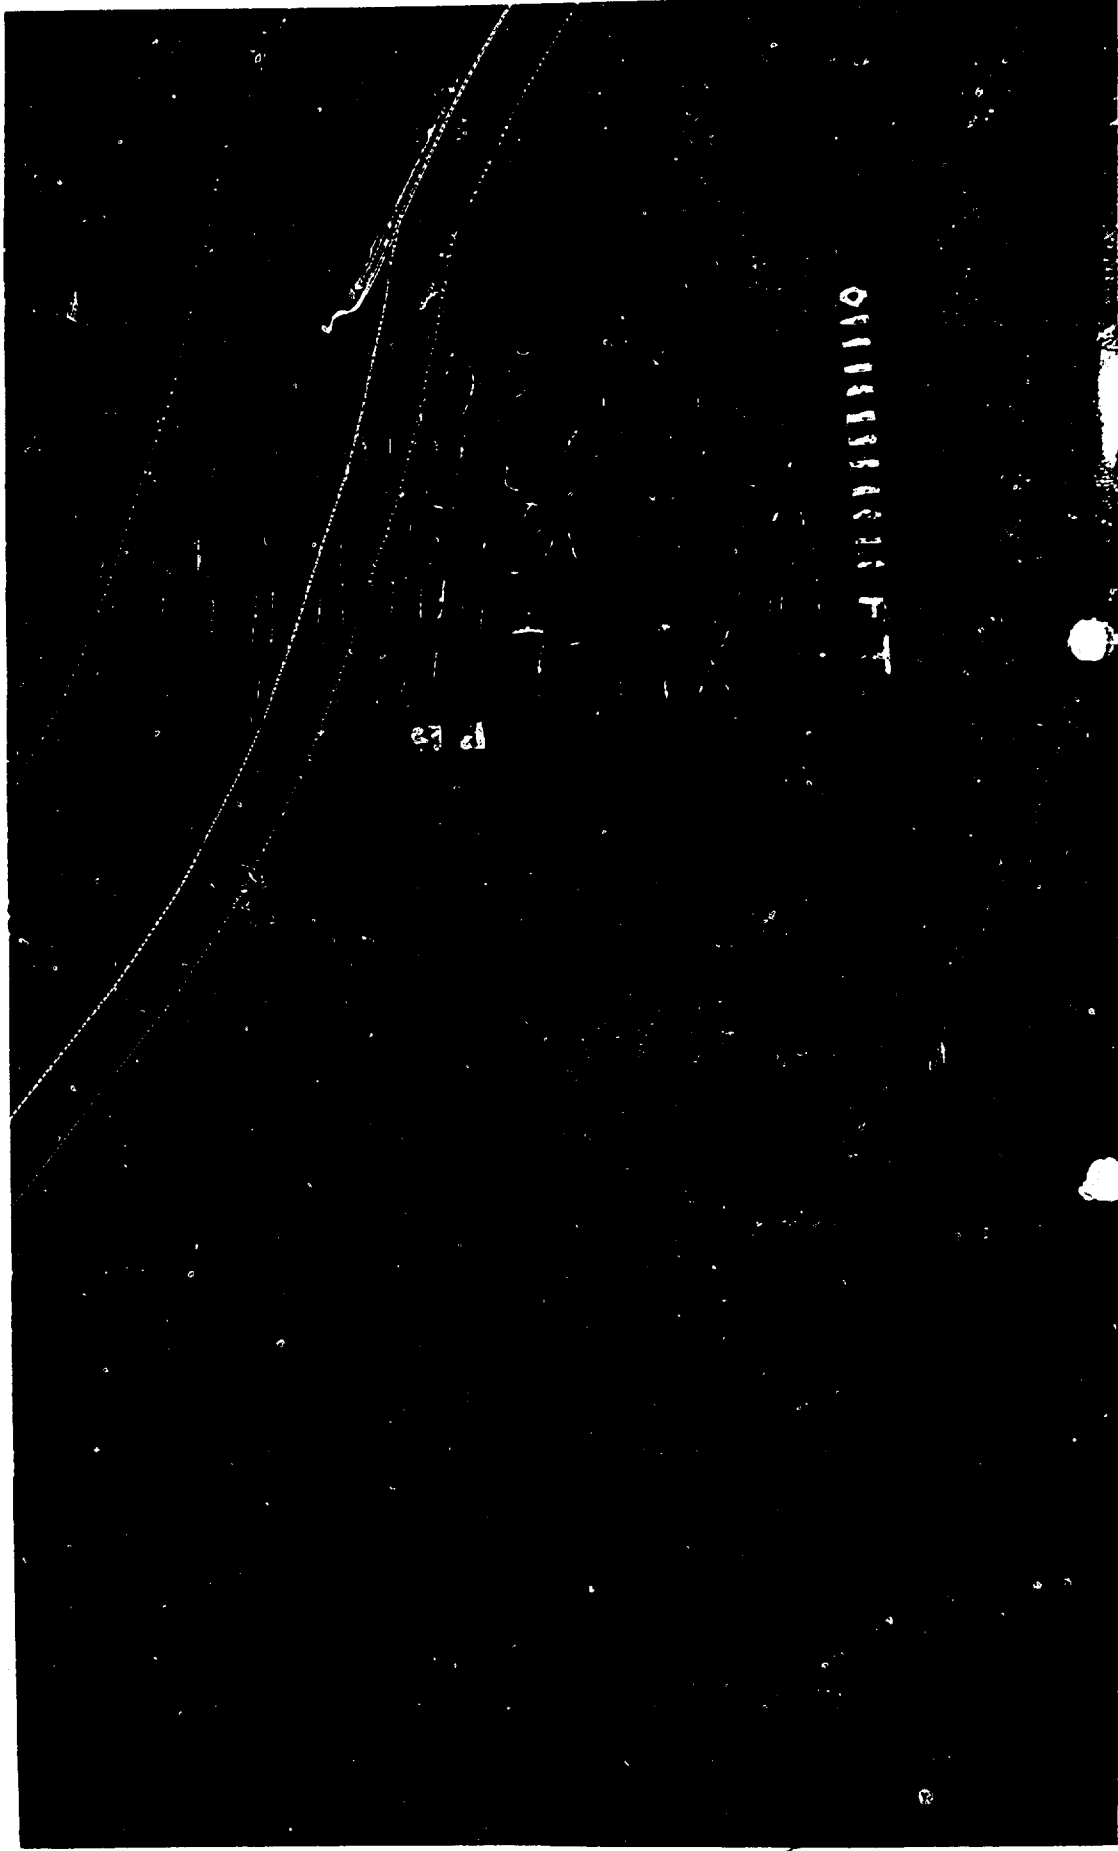

UN

Impact No.  
30530

Plate Thickness  
.98

Obliquity  
29° 50'

Striking Velocity  
1053 ft/sec.

No. of  
SK78841

Penetration  
complete

Remarks  
projectile  
effective  
nose chewed  
and ogive  
gouged.

15 March 1945



UNCLASSIFIED

Details for the ballistic tests are given below. Photographs of the projectiles and plates after impact are shown in Figure 6 and 7.

	<u>Round 1</u>	<u>Round 2</u>
NPG Impact No.	30720	30830
Plate Thickness	2.40	0.98
Obliquity	31°20'	29°50'
Striking Velocity	1052 ft/sec	1053 ft/sec
% of Sk.78841	112.5	198.8
Penetration	1/2"	Complete
Dish	1/2"	1"
Impact Dimensions	3" x 5"	6" x 10"
Thru Opening	None	6" x 9-1/2"
Proj. Condition	Completely broken up	Eff., Nose chewed, ogive gouged
	Projectile Wt. 119#, Inert Filler	

#### IV. DISCUSSION

The ballistic test shows this projectile to be greatly inferior to U.S. Navy 6" Common projectiles. After penetrating a 1" STS plate at 30° obliquity the Italian projectile had its nose chewed and the ogive gouged. This poor performance is due to two factors,

1. Inferior microstructure. Coarse pearlite and ferrite is a very undesirable structure when resistance to shock is desired. A microstructure of tempered martensite, necessary in order to obtain good ballistic performance, could not be obtained, in a projectile of this size with the plain carbon steel used.

2. Low hardness. Modern U.S. Navy common projectiles have a differentially hardened body with a nose hardness of from 600 to 620 VPN. The whole body of this Italian projectile is softer than the base of the U.S. Navy common projectile.

UNCLASSIFIED