

UNCLASSIFIED

AD NUMBER
AD419603
NEW LIMITATION CHANGE
TO Approved for public release, distribution unlimited
FROM Distribution authorized to U.S. Gov't. agencies and their contractors; Foreign Government Information; 1963. Other requests shall be referred to British Embassy, 3100 Massachusetts Avenue, NW, Washington, DC 20008.
AUTHORITY
DSTL, ADM 249/1013, 12 Aug 2008

THIS PAGE IS UNCLASSIFIED

UNCLASSIFIED

AD 419603

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA




UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

ACSIL/ADM/591/314A
ACC/H 4/7/62

ADMIRALTY CORROSION COMMITTEE
MACHINERY CORROSION SUB-COMMITTEE
HULL AND STRUCTURAL CORROSION SUB-COMMITTEE

CENTRAL DOCKYARD LABORATORY

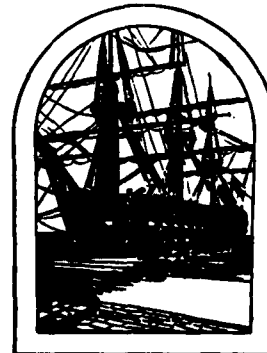

For permission to print any of the information contained in this report, please apply to the Admiralty, quoting the ACSIL No.

CATALOGUED BY DDC
AS AD No. _____

419603

C.D.L. REPORT

GOB

THE CORROSION OF STAINLESS STEELS AND
RELATED ALLOYS IN MARINE ENVIRONMENTS

PART II. RESULTS FOR FURTHER ALLOYS

DDC
RECEIVED
OCT 11 1962
RESOLVED
TISIA D

H.M. DOCKYARD,
PORTSMOUTH.

CENTRAL DOCKYARD LABORATORY
PORTSMOUTH

THE CORROSION OF STAINLESS STEELS AND RELATED ALLOYS
IN MARINE ENVIRONMENTS

PART II. RESULTS FOR FURTHER ALLOYS

SYNOPSIS

The corrosion behaviour of a number of stainless steels and high nickel alloys, additional to those given in C.D.L. Report GCF (ACC/N 196/59 (H 405)) are reported. The precipitation hardenable stainless steel FV.520, of particular interest due to its high strength, had only slightly improved corrosion resistance compared to the martensitic stainless steel En.57. The austenitic alloy Langalloy 11K behaved similarly to a normal ferritic steel with respect to the form of attack but with a reduced corrosion rate. No stainless alloy tested can be recommended to withstand full immersion crevice corrosion conditions.

INTRODUCTION

Since reporting the corrosion behaviour of commonly used stainless steels and high nickel alloys (1) a number of similar alloys, including a proprietary precipitation hardenable stainless steel, have been tested for their corrosion behaviour. The previous report concluded that such alloys had good intrinsic corrosion resistance in well aerated sea water but they were liable to severe local corrosion under crevice conditions. In the present series of tests it was the resistance to crevice corrosion which was principally investigated.

II. EXPERIMENTAL

The testing methods used involved an accelerated laboratory test for crevice corrosion, crevice corrosion tests in Langston Harbour, and plain corrosion tests in respect of one alloy. Accelerated tests were confined to specimens in bar form and comprised martensitic stainless steels, including a proprietary precipitation hardenable steel, austenitic stainless steels, chromium plated stainless steel, Nimonic 80, and Stellite. The Langston Harbour tests comprised similar stainless steels and a number of high nickel alloys. Plain corrosion tests were made on the proprietary manganese-aluminium austenitic steel Langalloy 11K.

In the accelerated test specimens, in bar form, were locally depassivated electrolytically and crevices quickly formed using tight polythene sleeves before exposure in a tank of sea water for 3 weeks. With this method, the time interval between depassivation and forming the crevice must be extremely short, otherwise the oxide film will re-heal.

The crevice corrosion tests in Langston Harbour were made under full immersion conditions, the exposure period being one year. The crevice was made by sandwiching half a 3 in. x 1 in. specimen between two pieces of perspex as described previously(1).

The plain corrosion specimens of the proprietary alloy Langalloy 11K were tested in the cold worked, annealed, and oxidised conditions (1 hour at 600°C in oxygen). In addition, the steady corrosion potentials of this alloy in sea water were measured with reference to a saturated calomel electrode.

III. RESULTS

Using the accelerated crevice corrosion test it was apparent that the martensitic stainless steel En.57 and the precipitation hardenable stainless steel FV.520 were readily susceptible to crevice corrosion regardless of the heat-treatment. Chromium plate up to a thickness of 4 thou. failed to prevent crevice corrosion as shown in Fig. 1. The results of this test for a number of alloys are shown in Table 1.

The extent of crevice corrosion on specimens exposed for one year in Langston Harbour are given in Table 2. It will be seen that all the martensitic stainless steels and monel were severely attacked. Austenitic stainless steels and high nickel alloys, other than monel, were only slightly attacked with the molybdenum containing alloys En.58J, FV.254 and Hastelloy 'C' giving the best results.

The plain corrosion rates of the Langalloy 11K after one years exposure and the measured corrosion potentials are shown in Table 3. It will be observed that the corrosion potential of Langalloy 11K is similar to that of mild steel (-0.65 volts) rather than a stainless steel (-0.1 to 0.2 volts) and consequently it is unlikely that the Langalloy 11K would be susceptible to crevice corrosion.

In the crevice corrosion tests the Langalloy 11K and the Corronel 'B' (66 Ni/28 Mo/6 Fe) corroded outside the creviced area.

IV. DISCUSSION AND CONCLUSIONS

The results given for further martensitic and austenitic stainless steels and high nickel alloys should be considered as an Addendum to C.D.L. Report GCF (ACC/N 196/59, ACC/H 405/59). The conclusions given in the earlier report are supported and in particular it may be noted that the precipitation hardenable stainless steel FV.520 behaved similarly to the martensitic steel En.57.

Apart from this general conclusion it may be noted that the crevice corrosion resistance of the hardenable stainless steels (En.57, and FV.520) varied significantly according to structure as well as chemical composition and that chromium plating had no beneficial effect.

Molybdenum bearing stainless steels were least attacked in the austenitic group and of these Rex 78 and FV.254 appeared to be slightly superior to En. 58J. The hard facing alloys (Stellites 1, 6 and 12) were comparable to austenitic stainless steels in their resistance to crevice corrosion.

In the high nickel alloys Ni-0-Nel and Hastelloy 'C' had much superior crevice corrosion resistance to Monel. Corronel 'B' was attacked outside the crevice and suffered a higher plain corrosion rate than other nickel alloys, tested under these conditions.

The austenitic alloy Langalloy 11K suffered general corrosion and behaved similarly to a mild steel with a third of the corrosion rate. The corrosion potential of this alloy (-0.79) is less basic than mild steel (-0.65 volts) and the possibility of its use coupled to aluminium alloys is being investigated.

Reference

- (1) The Corrosion Resistance of Stainless Steels and Relative Alloys in Marine Environments.

C.D.L. Report GCF (ACC/N 196/59, ACC/H 405/59).

- - - oOo - - -

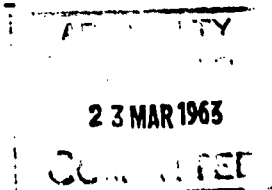


TABLE 1

SUSCEPTIBILITY OF ALLOYS TO CREVICE CORROSION
LABORATORY TESTS

MATERIAL	HARDNESS V.P.N.	% COMPOSITION NOMINAL, MAJOR ALLOYING ELEMENTS				EXTENT OF ATTACK
		C	Cr	Ni	Others	
<u>MARTENSITIC STAINLESS STEELS</u>						
En.57	258	0.16	16.5	2.4		Severe
En.57	300	0.16	16.5	2.4		Severe
FV.520 Soft	232	0.07	16	6	1½ Cu, 1½ Mo.	Severe
FV.520 Peak Hardness	392	0.07	16	6	1½ Cu, 1½ Mo.	Severe
FV.520 Overaged	310	0.37	16	6	1½ Cu, 1½ Mo.	Severe
<u>AUSTENITIC STAINLESS STEELS</u>						
En.58 J	-	0.07	18	10	3 Mo.	Very slight
En.58 F	-	0.08	18	10	1½ Cb.	Slight
G. 18 B	-	0.4	13	13	2 Mo, 2½ W, 10 Co, 3 Cb	Slight
FV.254	-	0.07	18	18	3½ Mo, 2½ Cu, ½ Ti	None
Langalloy 20V	-	0.04	20	30	3½ Mo, 4 Cu, 1 Cb	Slight
Rex 78	-	0.7	14	18	3½ Mo, 3½ Cu, ½ Ti	None
<u>HIGH NICKEL ALLOY</u>						
Nimonic 80	-	0.34	21	75	2½ Ti, ½ Al.	Severe
<u>HARD FACING ALLOYS</u>						
Stellite 1	-	-	34	-	43 Co, 14 W, 9 Fe.	None
Stellite 6	-	-	33	-	55 Co, 6 W, 7 Fe.	Slight
Stellite 12	-	-	34	-	47 Co, 10 W, 9 Fe.	Slight

TABLE 2

CREVICE CORROSION RATES OF STAINLESS STEELS
AND HIGH NICKEL ALLOYS

TESTS IN LANGSTON HARBOUR

MATERIAL	HARDNESS V.P.N.	% COMPOSITION NOMINAL. MAJOR ALLOYING ELEMENTS				CREVICE CORROSION RATE	
		C	Cr	Ni	Others	mg./crev. sq.dm./day	Average
<u>MARTENSITIC STAINLESS STEELS</u>							
En.57 Soft	252	0.16	16.5	2.4		42.2, 47.6, 37	42.3
En.57 Heat treated	348	0.16	16.5	2.4		41.8, 35.2, 35.2	37.4
FV.520 Soft*	232	0.06	14.4	5.3	1 $\frac{3}{4}$ Cu, 2 Mo.	16.4, 17.8, 7.8	14.0
FV.520 Peak Hardness*	385	0.06	14.4	5.3	1 $\frac{3}{4}$ Cu, 2 Mo.	11.2, 24.4, 13.8	16.5
FV.520 Overaged I*	301	0.06	14.4	5.3	1 $\frac{3}{4}$ Cu, 2 Mo.	37.6, 17.0, 30.0	29.2
FV.520 Overaged II*	315	0.06	14.4	5.3	1 $\frac{3}{4}$ Cu, 2 Mo.	27.4, 40.0	33.7
<u>AUSTENITIC STAINLESS STEELS</u>							
En.58J As Received	263	0.07	18	10	3 Mo.	0.02, 0.04, 0.46	0.2
En.58J Annealed	187	0.07	18	10	3 Mo.	0.6, 5.4, 5.4	3.8
FV.254	150	0.07	18	18	3 $\frac{1}{2}$ Mo, 2 $\frac{1}{2}$ Cu, $\frac{1}{2}$ Ti	0.02, 0.02, 0.08	0.04
Langalloy 20V	223	0.04	19.7	29.6	3 $\frac{1}{2}$ Mo, 4 Cu, 1 Cb	5.4, 7.0	6.2
<u>HIGH NICKEL ALLOYS</u>							
Monel	130	0.1	-	69	1 Fe, 30 Cu	16.6, 14.6, 16.6	15.9
Ni-O-Nel As Received	242	1.75	21	40	31 Fe, 3 Mo, 1 $\frac{3}{4}$ Cu	0.4, 3.8, 0.6	1.6
Ni-O-Nel Annealed	194	1.75	21	40	31 Fe, 3 Mo, 1 $\frac{3}{4}$ Cu	0.2, 3.0, 1.6	1.6
Hastelloy 'C'	210	-	15	58	17 Mo, 4 W, 6 Fe	0.03, 0.04	0.04

*Heat treatments:

Soft

1050°C Air Cooled

Peak Hardness 1050°C Air Cooled + 2 hours 750°C + 24 hours 15°C +
2 hours 450°C Air Cooled.

Overaged I 1050°C Air Cooled + 2 hours 750°C Air Cooled + 24 hours
15°C + 2 hours 560°C Air Cooled.

Overaged II 1050°C Air Cooled + 2 hours 850°C Air Cooled + 5 hours
450°C Air Cooled.


TABLE 3

THE CORROSION RATES AND CORROSION POTENTIAL OF LANGALLOY 11K

(C. 0.59, Si. 0.12, Mn. 22.05, Al. 8.80, Ni. 0.05, P. 0.020, S. 0.025, Fe. rem.)

Condition	Hardness VPN/30	Corrosion Rate mg./sq.dm./day		Corrosion potential with reference to saturated calomel half cell volts
		Individual Results	Average	
Cold Worked sheet	375	9.1, 9.9	9.5	- 0.79
Annealed sheet	287	8.8, 10.0	9.4	- 0.79
Oxidised sheet	-	10.0, 15.5	12.6	- 0.61

Corrosion rate of mild steel 30 mg./sq.dm./day
Corrosion rate of copper 8 mg./sq.dm./day

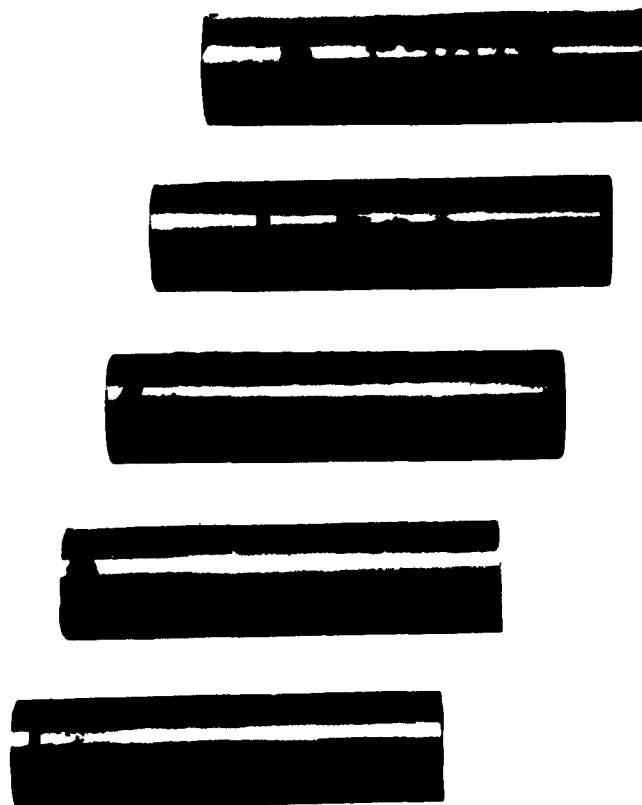

x 1

FIG. 1. Crevice corrosion produced by accelerated method on specimens.
 2 thou. Cr plate on FV.520, 4 thou. Cr plate on FV.520,
 FV.520 soft, FV.520 overaged, and FV.520 peak hardness,
 respectively.



*Information Centre
Knowledge Services*
[dstl] Porton Down
Salisbury
Wiltshire
SP4 0JQ
22060-6218
Tel: 01980-613753
Fax 01980-613970

Defense Technical Information Center (DTIC)
8725 John J. Kingman Road, Suit 0944
Fort Belvoir, VA 22060-6218
U.S.A.

AD#: AD419603

Date of Search: 12 August 2008

Record Summary: ADM 249/1013

Title: Corrosion of stainless steels and related alloys in marine environments: results for further alloys

Availability Open Document, Open Description, Normal Closure before FOI Act: 30 years

Former reference (Department) ACC H427/62

Held by The National Archives, Kew

This document is now available at the National Archives, Kew, Surrey, United Kingdom.

DTIC has checked the National Archives Catalogue website (<http://www.nationalarchives.gov.uk>) and found the document is available and releasable to the public.

Access to UK public records is governed by statute, namely the Public Records Act, 1958, and the Public Records Act, 1967.

The document has been released under the 30 year rule.

(The vast majority of records selected for permanent preservation are made available to the public when they are 30 years old. This is commonly referred to as the 30 year rule and was established by the Public Records Act of 1967).

This document may be treated as UNLIMITED.