

AD609372

REPORT NO. MECH-1

FIXED-WHEEL GATE BEARING STUDIES

Progress Report

by

G. I. Brooks, Principal Investigator

M. Lopez, Jr., Assisting Investigator

D. B. Mountjoy, Assisting Investigator

Mechanical Branch, Division of Design

Office of Chief Engineer



United States Department of the Interior
Bureau of Reclamation, Denver, Colorado

October 1, 1964

ABSTRACT

Tests to determine friction coefficients and bearing behavior in 3 types of bearings--2 self-lubricating and 1 plain bronze--show that increased allowable bearing pressures of 6,000 psi and a design coefficient of friction of 0.10 can be used for one of the self-lubricating-type wheel bearings (Type B). Antifriction roller bearings were studied because reductions in wheel-bearing friction forces gained from raising allowable bearing pressure may not always be sufficient to permit gravity closure. Although antifriction bearings cost more, there are circumstances in which the higher bearing cost could be offset by other overall design or economic considerations. Since bearings must support heavy radial loads as well as thrust loads, only tapered roller and self-aligning spherical roller bearings were studied. Self-aligning spherical roller bearings were chosen because the self-aligning feature compensates for deflections caused by hydraulic load and for installation and fabrication misalignments. Fixed-wheel gate design on one job using antifriction self-aligning spherical roller bearings saved 12,000 pounds of gate weight and 23,000 pounds in hoist capacity. Operation and maintenance experience from this gate will help evaluate reliability of these bearings.

DESCRIPTORS-- *fixed wheel gates / *bearings / *friction tests / closing / gate hoists / weight / bronze / stainless steel / corrosion / lubrication / design criteria / *friction / economies / underwater / bearing capacities / laboratory tests / coefficients / bearing values / corrosion control / submergence / gates / performance tests / wheels / reliability / horizontal loads / gate seals

IDENTIFIERS-- antifriction bearings / *bearing behavior / wheel loads / radial loads / thrust loads / *friction coefficients / self-aligning bearings / roller bearings / spherical roller bearings

INTRODUCTION

For fixed-wheel gates which are required to close by gravity, the frictional forces must be less than the gate weight. Extra weight has been added to some gates to insure closure, but this practice increases gate and hoist costs. Direct benefits can be derived by reducing gate friction forces.

Frictional forces on a fixed-wheel gate consist of seal friction, sliding friction of guide shoes, wheel rolling friction, and wheel bearing friction. Wheel bearing friction, which usually accounts for a large portion of the total, is calculated from the formula:

$$F = \frac{PfR_1}{R_2} = \frac{Pf}{R_2/R_1},$$

where

F = wheel frictional force
P = wheel load
f = coefficient of friction
R₁ = wheel pin radius
R₂ = wheel radius

The wheel frictional force, F, can be reduced by decreasing f and by increasing the wheel/pin ratio, R₂/R₁. R₂ is generally as large as the size of the gate and gate slot will permit and is, therefore, fixed for any particular installation. R₁, however, can be reduced if the bearing pressure between the bearing and the pin can be increased.

The purpose of this study is to determine economical means of reducing the wheel bearing friction.

STUDIES

Three general types of bearings were investigated: self-lubricating plain bearings, SAE 64 plain bronze bearings, and antifriction roller bearings. A study of the technical literature and catalogs of commercially available bearings indicated that two self-lubricating bronze bearings merited consideration. One of these self-lubricating bearings, Type B, has been used by the Bureau of Reclamation and has proved quite reliable for underwater service.

The manufacturers of the two self-lubricating-type bearings were contacted and supplied bearings for a test program performed by our Research Division. To evaluate the effectiveness of self-lubricating inserts properly, plain SAE 64 bronze bearings were also tested.

The Research Division tested the bearings and determined the coefficient of friction and bearing behavior at 2,700-, 4,000-, 6,000-, and 10,000-pounds-per-square-inch bearing pressure (based on projected area) for the following lubrication conditions:

1. Ungreased, dry
2. Greased, dry
3. Ungreased, submerged in water
4. Greased, submerged in water

The results are summarized in Table 1. These results indicate that the Type B bearings have a lower coefficient of friction than Type A or plain bronze. Their performance indicates that the allowable bearing pressure can be raised from 4,000 to 6,000 pounds per square inch, thereby permitting an increase in the wheel/pin ratio and reducing the wheel bearing frictional force. The design coefficient of friction, however, will be kept at 0.10 to allow for possible misalignment in installation and the effects of foreign materials and age on the bearings.

Since the reductions in wheel bearing frictional forces gained from raising the allowable bearing pressure may not always be sufficient to permit gravity closure, a study of anti-friction roller bearings was undertaken. Despite the recognized higher cost of anti-friction roller bearings, the study was initiated as there are circumstances in which the higher bearing cost could be offset by other overall design or economic considerations.

As the bearings must withstand thrust loads in addition to heavy radial loads, only tapered roller and self-aligning spherical roller bearings were investigated. Layouts indicated spherical roller bearings offered advantages over tapered roller bearings, as the self-aligning feature compensates for deflections caused by the hydraulic load on the gate and for fabrication and installation misalignments of the gate and track. The coefficient of friction for either type would be the same; and while a precise value was not checked, a coefficient of 0.01 was used as it is deemed conservative enough to cover some of the variables involved in submerged installations.

To minimize the possibility of bearing failure due to corrosion, AISI 440-C stainless steel, which has excellent corrosion resistance and can be heat treated to give capacities similar to those of conventional bearing steels, was used for the bearings. A tangential seal operating on a spherical seal seat excludes water from the bearing and retains grease while permitting the wheel and outer bearing race an angular misalignment rotation of plus or minus 1-1/2°.

To facilitate field installation, a pedestal type of wheel assembly was developed (see Figure 1), which can be completely shop assembled and shipped as a unit. This design makes it possible to keep the bearing clean by eliminating field assembly of the wheel bearing parts. It also provides an easy method of alignment of the wheel surfaces by shimming under the pedestals.

RESULTS

The studies indicated that a design bearing pressure of 6,000 pounds per square inch on the projected bearing area can be used for Type B bearings. Small savings in weight have been made by using the higher bearing pressures on the penstock gates for Yellowtail Dam, purchased under Invitation No. DS-6039, and on the penstock gates, Invitation No. DS-6179, for Morrow Point Dam.

The studies of the anti-friction roller bearings indicated that use of anti-friction wheel bearings will permit practically any gate to close by gravity without the addition of supplemental weight. Anti-friction bearings were used on the fixed-wheel gates for the Main Canal Headworks, Navajo Indian Irrigation Project, Invitation No. DS-6087, resulting in elimination of 12,000 pounds of supplemental cast-iron weights which would have been necessary to close the gate by gravity. In addition, the hoist capacity was reduced by 23,000 pounds. The operating and maintenance experience gained at this installation will be employed in evaluating the reliability of anti-friction bearings and the service required to keep them in proper working order.

FURTHER STUDY

Recently a new bearing using fluoro-carbon fabric bonded to a steel backing has been developed. These bearings appear to have the advantage of high bearing capacity and reduced coefficient of friction. It is planned to test and evaluate these bearings.

ACKNOWLEDGEMENTS


The Division of Research in the Office of Chief Engineer, Denver, Colorado, performed the laboratory testing of the self-lubricating and SAE 64 bronze bearings.

REFERENCE

1. "Fixed-wheel Gates for Penstock Intakes," Journal of Power Division, ASCE, October 1957, pp. 1420-4, S. J. Skinner.

SUMMARY OF FRICTION TESTS OF SELF-LUBRICATING BEARINGS
 TYPES A AND B, AND SAE 64 BRONZE BEARINGS
 Coefficients of Friction

Bushing	Lubrication	Bearing pressure, pounds per square inch				Condition at end of test
		2,700	4,050	6,000	10,000	
Type A Type B SAE 64	Dry Dry Dry	0.043-0.097	0.079-0.107	0.084-0.154	0.095-0.162	Bad scoring Slight scoring Seized at 6,000 pounds per square inch
		.048-.076	.060-.069	.040-.066	.044-.067	
		.077-.173	.102-.186	--	--	
Type A Type B SAE 64	Greased Greased Greased	.007-.047	.023-.061	.068-.134	.056-.130	Some scoring Smooth Slight scoring
		.014-.033	.013-.047	.015-.064	.030-.062	
		.060-.080	.046-.091	.093-.129	.073-.126	
Type A Type B SAE 64	Submerged in water	.081-.145	.101-.127	.072-.125	.065-.131	Good Slight score Scored
		.029-.057	.016-.056	.028-.056	.034-.051	
Type A Type B SAE 64	Greased and submerged in water	No test	No test	.088-.149	.074-.174	OK OK OK
		.050-.062	.061-.070	.074-.123	.077-.120	
Type A Type B SAE 64	Greased and submerged in water	.016-.042	.034-.051	.017-.044	.030-.056	OK OK OK
		.045-.097	.048-.094	.072-.139	.081-.123	

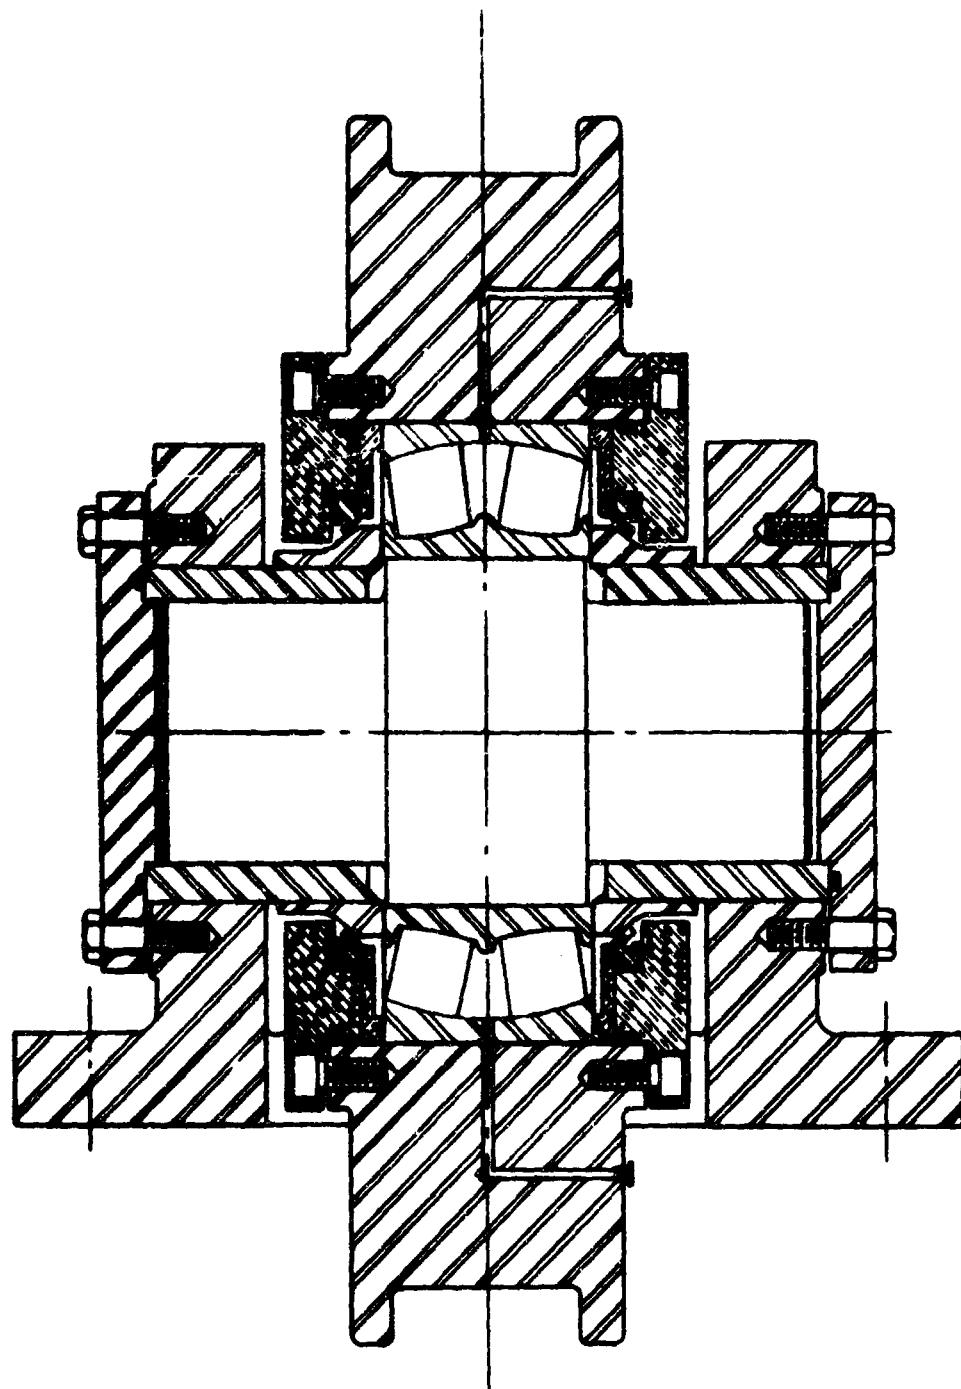

WHEEL ASSEMBLY
9- BY 12-FOOT FIXED-WHEEL GATE
MAIN CANAL HEADWORKS
NAVAJO INDIAN IRRIGATION PROJECT

Figure 1

CPD 646-488

ABSTRACT

Tests to determine friction coefficients and bearing behavior in 3 types of bearings--2 self-lubricating and 1 plain bronze--show that increased allowable bearing pressures of 6,000 psi and a design coefficient of friction of 0.10 can be used for one of the self-lubricating-type wheel bearings (Type B). Antifriction roller bearings were studied because reductions in wheel-bearing friction forces gained from raising allowable bearing pressures may not always be sufficient to permit gravity closure. Although antifriction bearings cost more, there are circumstances in which the higher bearings cost could be offset by other overall design or economic considerations. Since bearings must support heavy radial loads as well as thrust loads, only tapered roller and self-aligning spherical roller bearings were studied. Self-aligning spherical roller bearings were chosen because the self-aligning feature compensates for deflections caused by hydraulic load and for installation and fabrication misalignments. Fixed-wheel gate design on one job using antifriction self-aligning spherical roller bearings saved 12,000 pounds of gate weight and 23,000 pounds in hoist capacity. Operation and maintenance experience from this gate will help evaluate reliability of these bearings.

ABSTRACT

Tests to determine friction coefficients and bearing behavior in 3 types of bearings--2 self-lubricating and 1 plain bronze--show that increased allowable bearing pressures of 6,000 psi and a design coefficient of friction of 0.10 can be used for one of the self-lubricating-type wheel bearings (Type B). Antifriction roller bearings were studied because reductions in wheel-bearing friction forces gained from raising allowable bearing pressures may not always be sufficient to permit gravity closure. Although antifriction bearings cost more, there are circumstances in which the higher bearings cost could be offset by other overall design or economic considerations. Since bearings must support heavy radial loads as well as thrust loads, only tapered roller and self-aligning spherical roller bearings were studied. Self-aligning spherical roller bearings were chosen because the self-aligning feature compensates for deflections caused by hydraulic load and for installation and fabrication misalignments. Fixed-wheel gate design on one job using antifriction self-aligning spherical roller bearings saved 12,000 pounds of gate weight and 23,000 pounds in hoist capacity. Operation and maintenance experience from this gate will help evaluate reliability of these bearings.

ABSTRACT

Tests to determine friction coefficients and bearing behavior in 3 types of bearings--2 self-lubricating and 1 plain bronze--show that increased allowable bearing pressures of 6,000 psi and a design coefficient of friction of 0.10 can be used for one of the self-lubricating-type wheel bearings (Type B). Antifriction roller bearings were studied because reductions in wheel-bearing friction forces gained from raising allowable bearing pressures may not always be sufficient to permit gravity closure. Although antifriction bearings cost more, there are circumstances in which the higher bearings cost could be offset by other overall design or economic considerations. Since bearings must support heavy radial loads as well as thrust loads, only tapered roller and self-aligning spherical roller bearings were studied. Self-aligning spherical roller bearings were chosen because the self-aligning feature compensates for deflections caused by hydraulic load and for installation and fabrication misalignments. Fixed-wheel gate design on one job using antifriction self-aligning spherical roller bearings saved 12,000 pounds of gate weight and 23,000 pounds in hoist capacity. Operation and maintenance experience from this gate will help evaluate reliability of these bearings.

ABSTRACT

Tests to determine friction coefficients and bearing behavior in 3 types of bearings--2 self-lubricating and 1 plain bronze--show that increased allowable bearing pressures of 6,000 psi and a design coefficient of friction of 0.10 can be used for one of the self-lubricating-type wheel bearings (Type B). Antifriction roller bearings were studied because reductions in wheel-bearing friction forces gained from raising allowable bearing pressures may not always be sufficient to permit gravity closure. Although antifriction bearings cost more, there are circumstances in which the higher bearings cost could be offset by other overall design or economic considerations. Since bearings must support heavy radial loads as well as thrust loads, only tapered roller and self-aligning spherical roller bearings were studied. Self-aligning spherical roller bearings were chosen because the self-aligning feature compensates for deflections caused by hydraulic load and for installation and fabrication misalignments. Fixed-wheel gate design on one job using antifriction self-aligning spherical roller bearings saved 12,000 pounds of gate weight and 23,000 pounds in hoist capacity. Operation and maintenance experience from this gate will help evaluate reliability of these bearings.

MECH-1
Brooks, G. I.; Lopez, M. Jr.; and Mountjoy, D. B.
FIXED-WHEEL GATE BEARING STUDIES
Bureau of Reclamation, Denver, 4 pages, 1 table, 1 figure, 1964

DESCRIPTORS-- *fixed wheel gates / *bearings / *friction tests / closing / gate hoists / weight / bronze / stainless steel / corrosion / lubrication / design criteria / *friction / economies / underwater / bearing capacities / laboratory tests / coefficients / bearing values / corrosion control / submergence / gates / performance tests / wheels / reliability / horizontal loads / gate seals

IDENTIFIERS-- *antifriction bearings / *bearing behavior / wheel loads / radial loads / thrust loads / *friction coefficients / self-aligning bearings / roller bearings / spherical roller bearings

MECH-1
Brooks, G. I.; Lopez, M. Jr.; and Mountjoy, D. B.
FIXED-WHEEL GATE BEARING STUDIES
Bureau of Reclamation, Denver, 4 pages, 1 table, 1 figure, 1964

DESCRIPTORS-- *fixed wheel gates / *bearings / *friction tests / closing / gate hoists / weight / bronze / stainless steel / corrosion / lubrication / design criteria / *friction / economies / underwater / bearing capacities / laboratory tests / coefficients / bearing values / corrosion control / submergence / gates / performance tests / wheels / reliability / horizontal loads / gate seals

IDENTIFIERS-- *antifriction bearings / *bearing behavior / wheel loads / radial loads / thrust loads / *friction coefficients / self-aligning bearings / roller bearings / spherical roller bearings

MECH-1
Brooks, G. I.; Lopez, M. Jr.; and Mountjoy, D. B.
FIXED-WHEEL GATE BEARING STUDIES
Bureau of Reclamation, Denver, 4 pages, 1 table, 1 figure, 1964

DESCRIPTORS-- *fixed wheel gates / *bearings / *friction tests / closing / gate hoists / weight / bronze / stainless steel / corrosion / lubrication / design criteria / *friction / economies / underwater / bearing capacities / laboratory tests / coefficients / bearing values / corrosion control / submergence / gates / performance tests / wheels / reliability / horizontal loads / gate seals

IDENTIFIERS-- *antifriction bearings / *bearing behavior / wheel loads / radial loads / thrust loads / *friction coefficients / self-aligning bearings / roller bearings / spherical roller bearings

MECH-1
Brooks, G. I.; Lopez, M. Jr.; and Mountjoy, D. B.
FIXED-WHEEL GATE BEARING STUDIES
Bureau of Reclamation, Denver, 4 pages, 1 table, 1 figure, 1964

DESCRIPTORS-- *fixed wheel gates / *bearings / *friction tests / closing / gate hoists / weight / bronze / stainless steel / corrosion / lubrication / design criteria / *friction / economies / underwater / bearing capacities / laboratory tests / coefficients / bearing values / corrosion control / submergence / gates / performance tests / wheels / reliability / horizontal loads / gate seals

IDENTIFIERS-- *antifriction bearings / *bearing behavior / wheel loads / radial loads / thrust loads / *friction coefficients / self-aligning bearings / roller bearings / spherical roller bearings