

AD A031639

TECHNICAL  
LIBRARY

WVT-TR-76037

AD

PERFORMANCE OF CHROME-PLATED 105MM M68 GUN  
TUBES WITH DISCARDING SABOT AMMUNITION

Allan A. Albright  
Glenn S. Friar  
Steven L. Morris

September 1976



**BENET WEAPONS LABORATORY**  
**WATERVLIET ARSENAL**  
**WATERVLIET, N.Y. 12189**

**TECHNICAL REPORT**

AMCMS No. 3110.15.1100

Pron No. T1-5-59363-01-33-M7

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

DISPOSITION

Destroy this report when it is no longer needed. Do not return it to the originator.

DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

| REPORT DOCUMENTATION PAGE  |                           | READ INSTRUCTIONS<br>BEFORE COMPLETING FORM   |
|--|---------------------------|---|
| 1. REPORT NUMBER<br>WVT-TR-76037   | 2. GOVT ACCESSION NO.     | 3. RECIPIENT'S CATALOG NUMBER   |
| 4. TITLE (and Subtitle)<br>PERFORMANCE OF CHROME-PLATED 105MM M68 GUN TUBES WITH DISCARDING SABOT AMMUNITION   |                           | 5. TYPE OF REPORT & PERIOD COVERED  |
|  |                           | 6. PERFORMING ORG. REPORT NUMBER  |
| 7. AUTHOR(s)<br>Allan A. Albright<br>Glenn S. Friar<br>Steven L. Morris  |                           | 8. CONTRACT OR GRANT NUMBER(s)  |
| 9. PERFORMING ORGANIZATION NAME AND ADDRESS<br>Benet Weapons Laboratory<br>Watervliet Arsenal, Watervliet, NY 12189<br>SARWV-RDT   |                           | 10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS<br>AMCMS 3110.15.1100<br>PRON T1-5-59363-01-33-M7 |
| 11. CONTROLLING OFFICE NAME AND ADDRESS<br>Project Manager, M60 Tank Development<br>ATTN: AMCPM-M60TD/AMSTA-EBM<br>Warren, MI 48092  |                           | 12. REPORT DATE<br>September 1976   |
|  |                           | 13. NUMBER OF PAGES<br>44   |
| 14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)<br>US Army Armament Command<br>Rock Island, IL 61201   |                           | 15. SECURITY CLASS. (of this report)<br><br>UNCLASSIFIED  |
|  |                           | 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE  |
| 16. DISTRIBUTION STATEMENT (of this Report)<br><br>Approved for public release; distribution unlimited.  |                           |   |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)   |                           |   |
| 18. SUPPLEMENTARY NOTES  |                           |   |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number)   |                           |   |
| Chrome plating   | Chrome plated gun barrels | Ordnance  |
| Wear resistance  | Ammunition                | Coating   |
| Guns   | Wear                      |   |
| Tanks (Combat Vehicles)  | Erosion                   |   |
| Gun barrels  | Ammunition dispersion     |   |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number)  |                           |   |
| <p>This report describes testing to determine the feasibility of chrome plating the bore of 105mm M68 Gun Tubes to reduce wear conditions which affect performance of the M392A2 Armor Piercing Discarding Sabot (APDS) Projectile and similar rounds. Two chrome plated tubes were prepared and, with a standard tube for control, fired to monitor relative performance. Based on several factors, it is concluded that special characteristics and sensitivities of M392-type projectiles result in a tendency toward degraded performance in chrome plated tubes. (over)</p> |                           |   |

20. ABSTRACT (Continued)

Recommendations are made to defer use of chrome plating in the M68 until factors affecting performance are fully identified through an exploratory development program.

## ACKNOWLEDGEMENT

The authors gratefully acknowledge the efforts and cooperation of the many individuals who contributed to the performance evaluation described in this report. Mr. Albert Schumacher and Mr. James Cerqua, Watervliet Arsenal Operations Directorate, assisted in preparing the gun tubes for testing. Mr. V. Peter Greco, Benet Weapons Laboratory Research Directorate, administered the bore plating operation. Mr. J. William Schweiker, Benet Weapons Laboratory Development and Engineering Directorate, assisted in interpreting and reducing the test firing data.

## TABLE OF CONTENTS

|  | PAGE |
|--|------|
| REPORT DOCUMENTATION PAGE, DD FORM 1473          |      |
| ACKNOWLEDGEMENT                                  | i    |
| INTRODUCTION                                     | 1    |
| BACKGROUND                                       | 3    |
| DESCRIPTION OF TEST                              | 5    |
| FIRING RECORD                                    | 7    |
| ANALYSIS OF DATA                                 | 11   |
| CORRECTED IMPACT DATA                            | 13   |
| FILM DATA  | 17   |
| CONCLUSIONS                                      | 25   |
| RECOMMENDATIONS                                  | 26   |
| APPENDIX A: STAR GAUGE AND BORESCOPE INSPECTIONS | 27   |
| APPENDIX B: PROJECTILE FLIGHT CHARACTERIZATIONS  | 32   |

## LIST OF ILLUSTRATIONS

| <u>FIGURE</u>  | PAGE |
|--|------|
| 1. SECTIONAL VIEW OF TYPICAL APDS-T<br>PROJECTILE                                    | 12   |
| 2. TARGET IMPACTS--FULL LENGTH PLATED TUBE   | 14   |
| 3. TARGET IMPACTS--PARTIAL LENGTH PLATED TUBE  | 15   |
| 4. TARGET IMPACTS--UNPLATED TUBE   | 16   |
| 5. CENTERING BAND INTERFERENCE AT 22.5 FEET (6.858M)--<br>FULL LENGTH PLATED TUBE    | 18   |
| 6. SUBPROJECTILE YAW OVER 8° AT 50 FEET (15.24M)--<br>FULL LENGTH PLATED TUBE        | 19   |
| 7. CENTERING BAND INTERFERENCE AT 22.5 FEET (6.858M)--<br>PARTIAL LENGTH PLATED TUBE | 20   |
| 8. LATE PETAL DISCARD AT 50 FEET (15.24M)--PARTIAL<br>LENGTH PLATED TUBE             | 21   |
| 9. CENTERING BAND INTERFERENCE AT 22.5 FEET (6.858M)--<br>UNPLATED TUBE              | 22   |
| 10. YAW OVER 8° AT 50 FEET (15.24M)--UNPLATED TUBE                                   | 23   |

## LIST OF TABLES

| <u>TABLE</u>   | PAGE |
|--|------|
| 1. HORIZONTAL AND VERTICAL IMPACT DISPERSION   | 8    |
| 2. MUZZLE VELOCITIES   | 9    |
| 3. CIRCULAR IMPACT ERRORS  | 17   |
| 4. TARGET IMPACT DISPERSIONS WITH CENSORING OF<br>ABNORMAL PROJECTILE FLIGHT IMPACTS | 24   |
| A1. STAR GAUGE MEASUREMENTS AT COMPLETION OF<br>TESTING--FULL LENGTH PLATED TUBE     | 29   |
| A2. STAR GAUGE MEASUREMENTS AT COMPLETION OF<br>TESTING--PARTIAL LENGTH PLATED TUBE  | 30   |
| A3. STAR GAUGE MEASUREMENTS AT COMPLETION OF<br>TESTING--UNPLATED TUBE               | 31   |
| B1. PROJECTILE FLIGHT CHARACTERISTICS--FULL<br>LENGTH PLATED TUBE                    | 33   |
| B2. PROJECTILE FLIGHT CHARACTERISTICS--PARTIAL<br>LENGTH PLATED TUBE                 | 34   |
| B3. PROJECTILE FLIGHT CHARACTERISTICS--UNPLATED TUBE                                 | 35   |



## INTRODUCTION

This report describes the results of recent testing to evaluate the performance of spin stabilized, armor piercing, discarding sabot (APDS) ammunition in chrome-plated 105mm M68 gun tubes. Earlier tests have indicated that, while chrome plating can significantly retard bore wear rates, there is a tendency toward degraded APDS accuracy in plated tubes.

Chrome plating has been considered as a deterrent to the evolution of secondary wear signatures in the M68 tube. Secondary wear is a highly variable erosion condition observed in the first 12 inches of rifled length. Early in tube life, this wear is observed as a diametral expansion at the origin of rifling (O.R.), followed by a contraction and a second expansion before tapering to negligible wear with increasing distance from the O.R. Conditions in the region of this second diametral expansion are called secondary wear. Later in life, the wear expansion starts at the O.R. and increases to a maximum level between 8 and 12 inches forward of the O.R. before tapering out to negligible wear. The point of maximum down-bore expansion is also called secondary wear.

Secondary wear is the result of erosive characteristics of HEAT-type ammunition. The normal consumption of ammunition in field use has been approximately 73% HEAT, 26% HEP and less than 1% APDS. HEP-type ammunition has a very small erosive effect, with a corresponding tube wear life greater than 15,000 rounds. In view of the large proportion of

HEAT-type ammunition consumed, it is apparent why field surveys have shown secondary wear to be prevalent in fielded M68 tubes. APDS ammunition also creates secondary wear, but it is insignificant in comparison to the HEAT-type erosion.<sup>1</sup>

Extensive accuracy firing tests with production tubes have shown that APDS ammunition is sensitive to secondary wear conditions, with drastically degraded performance occurring under certain conditions.<sup>2</sup> Resolution of accuracy considerations is a necessary prerequisite to the use of chrome plating as a solution to secondary wear problems.

---

<sup>1</sup>Watervliet Arsenal Report No. WVT-TR-75047, Analysis of Wear Data from 105mm M68 Gun Tubes in Field Service, July 1975.

<sup>2</sup>Aberdeen Proving Ground Report No. FR-P-82476, 22 April 1975.

## BACKGROUND

In 1959 and 1960, the United Kingdom tested one 105mm and four 20-pounder chrome-plated gun tubes for firing accuracy. The conclusion from this limited testing was that, while accuracy was not as good in an unplated control tube, it did improve as the unplated tube wore. The accuracy of the plated tubes remained constant.<sup>3,4</sup> In 1962, Watervliet Arsenal chrome plated three 105mm T254 tubes for accuracy testing. Test results indicated that the plated tubes gave poorer accuracy performance than unplated tubes.<sup>5</sup>

Recent testing, in which the 105mm M68 gun tube has been used as a vehicle to evaluate platings, indicates that an M68 tube plated with a 0.010 inch thick layer of chrome will develop negligible origin of rifling wear and minor secondary wear, when firing HEAT-type ammunition. Thus, since chrome plating has demonstrated the potential for reducing secondary wear conditions, the possibility of degraded accuracy performance with APDS ammunition is the determining factor for incorporating chrome plating in the M68 gun tube.

The remainder of this report will describe the special test program, administered by Watervliet Arsenal, to evaluate the accuracy potential of APDS ammunition in chrome-plated M68 gun tubes. This program was designed and implemented as the preliminary phase in the development

---

<sup>3</sup>Ordnance Board Proceeding, Q8837, 16 June 1959.

<sup>4</sup>Minutes of Meeting at RARDE, FPA/16/02, November 1960.

<sup>5</sup>USA TECOM Report No. DPS-469, Accuracy and Erosion Studies of Modified T254 Series Gun Tubes for 105mm Gun, M68, APG, 1962.

of wear resistant coatings for the M68 tube. Three possible outcomes of this phase were projected. First, chrome plating could show no adverse effect on accuracy. Given this outcome, a full-scale Product Improvement Project (PIP) for production plating would be initiated. Second, the chrome plate configuration could be found less than optimum, necessitating a major research and development program to prepare an alternate plating. Third, disadvantages or shortcomings of plated tubes could be found to outweigh any advantage they might offer, and the program would be dropped as a solution to APDS erratic performance.

## DESCRIPTION OF TEST

Originally, accuracy testing was to consist of comparing a standard production tube, a tube with full bore length chrome plating, and a third tube with full bore length chrome plating over an intermediate cobalt alloy plating. Due to anticipated limitations in the availability of production quantities of cobalt alloy, the intermediate cobalt alloy plated tube was not prepared for testing, being replaced by a tube with a partial length chrome plating. A partial length plated tube offers several advantages in production, including reduced cost and process time. Also, with the possibility of frictional interaction between the bore surface and APDS projectiles strongly influencing dispersion characteristics, the partial length plating presents less chromed bore surface area, while maintaining a wear resistant surface in the region of secondary wear.

Two 105mm M68 gun tubes were prepared under the supervision of the Physical Science Division, Benet Weapons Laboratory. A 0.010 inch thick chrome plating was applied to the full length of the bore of the first tube and chrome plate from the forcing cone to a distance of thirty inches into the rifled region of the bore in the second tube. Final bore diameters of both tubes were that of production tubes. These two tubes, and a standard production tube, were delivered to Aberdeen Proving Ground (APG), Maryland in February 1976.

Accuracy firing was conducted by the Materiel Test Directorate during March and April 1976.<sup>6</sup> Three replications, each consisting of a ten round group from each of the three test tubes, were conducted to measure target dispersion. All ammunition used in the test was Cartridge, 105mm: APDS-T M392A2, from Lot MA 9-4 (MPTS Lot FLP-2-2-71), conditioned to +70°F (+21.11°C). This ammunition lot was chosen as typical of United States production service ammunition. All rounds were fired at a 20-by-20-foot (6.096-by-6.096 meter) vertical target at a range of 1,000 meters. Recorded data included target impacts, muzzle velocity, wind velocity and direction, and smear camera photographs, at 22.5 and 50 feet (6.858 and 15.240 meters) from the muzzle, for each round fired. Prior to initiation of the test, a 10 mph (16 kmh) wind velocity limit was specified.

Replications were performed on 23 March 1976, 29 March 1976, and 6 April 1976. A representative from Watervliet Arsenal was present for the 23 March firing. The firing record and subsequent data analysis are discussed in the following two sections.

---

<sup>6</sup>USA TECOM Report No. APG-MT-4802, Product Improvement Test of Gun Tube, 105mm M68 Tube Wear Resistant Plating Accuracy Phase, APG, May 1976, referred to hereafter as USA TECOM Report No. APG-MT-4802.

## FIRING RECORD

Firing data is detailed in the report prepared by APG.<sup>7</sup> Table 1 is excerpted from this report and shows horizontal and vertical standard deviations of the impact coordinates for each ten round group.

Two-way analysis of variance (ANOVA) and F-tests on variance ratios (pooled over replicates) are unable to detect significant differences among horizontal standard deviations at the 5% level. No significant differences among vertical standard deviations are detected using two-way ANOVA. The F-test detects a just significant difference between the pooled standard deviations for CHR 2 (partial plate) and CHR 3 (unplated). This can be attributed to the 0.76 mil vertical standard deviation for CHR 2 in the first replicate.

Muzzle velocities, and associated standard deviations in velocities, for each tube and replicate are shown in Table 2. Significant differences in velocities, at the 5% level, can be shown to exist among tubes and among replicates. The average velocity of CHR 1 (full length) was significantly higher than that of CHR 3 (unplated) and the average velocity of CHR 1 and CHR 2, taken together, was significantly higher than that of CHR 3. The average velocity for the second replicate was significantly higher than both the first and third replicates, taken together or separately. At the 10% level, ANOVA failed to detect any significant differences among the velocity standard deviations for the three tubes.

---

<sup>7</sup>USA TECOM Report No. APG-MT-4802.

TABLE 1. HORIZONTAL AND VERTICAL IMPACT DISPERSION

| <u>TUBE</u>           | <u>FIRST</u> |              | <u>SECOND</u> |              | <u>THIRD</u> |              |
|-----------------------|--------------|--------------|---------------|--------------|--------------|--------------|
|                       | <u>HOR.*</u> | <u>VERT.</u> | <u>HOR.</u>   | <u>VERT.</u> | <u>HOR.</u>  | <u>VERT.</u> |
|                       | <u>S. D.</u> | <u>S. D.</u> | <u>S. D.</u>  | <u>S. D.</u> | <u>S. D.</u> | <u>S. D.</u> |
| ∞                     | 0.38         | 0.35         | 0.18          | 0.43         | 0.36         | 0.48         |
| CHR 1 (Full Plate)    | .45          | .76          | .19           | .33          | .45          | .27          |
| CHR 2 (Partial Plate) | .28          | .25          | .42           | .37          | .17          | .42          |

\* All values in MILS.



TABLE 2. MUZZLE VELOCITIES

| <u>TUBE</u>           | FIRST REPLICATE   |                  | SECOND REPLICATE  |                  | THIRD REPLICATE   |                  |
|-----------------------|-------------------|------------------|-------------------|------------------|-------------------|------------------|
|                       | AVERAGE           | S. D.            | AVERAGE           | S. D.            | AVERAGE           | S. D.            |
|                       | <u>fps (mps)</u>  | <u>fps (mps)</u> | <u>fps (mps)</u>  | <u>fps (mps)</u> | <u>fps (mps)</u>  | <u>fps (mps)</u> |
| CHR 1 (Full Plate)    | 4888<br>(1489.86) | 6.1<br>(1.859)   | 4902<br>(1494.13) | 6.3<br>(1.920)   | 4889<br>(1490.17) | 16.4<br>(4.999)  |
| CHR 2 (Partial Plate) | 4883<br>(1488.64) | 17.3<br>(5.273)  | 4900<br>(1493.52) | 8.6<br>(2.621)   | 4887<br>(1489.56) | 14.4<br>(4.389)  |
| CHR 3 (Control)       | 4885<br>(1488.94) | 10.4<br>(3.170)  | 4890<br>(1490.47) | 8.9<br>(2.713)   | 4882<br>(1489.03) | 10.2<br>(3.109)  |

Each of the three gun tubes in the test sustained a total of thirty-seven rounds; one proof round, the three ten round groups, and two warmer rounds prior to each ten round group. Star gauge measurement and borescope inspection were performed after proof firing and after the completion of firing. A summary of these results is in Appendix A. Progressive chipping, flaking, and stripping of chrome in the full plate tube (CHR 1) was noted in the two inspections performed on this tube.

## ANALYSIS OF DATA

Upon completion of test firings, additional data analysis was conducted at Watervliet Arsenal to prepare a qualitative assessment of the performance of the three gun tubes involved in the test. In this analysis, emphasis was placed on the relative performance of the three tubes, including segregation of ammunition related performance factors.

Figure 1 shows a cross-sectional view typical of the projectile in the M392/M724/M728 models of discarding sabot ammunition. A variety of parameters have been identified as related to the flight characteristics of this projectile, including frictional interfaces between the rotating and centering bands and the gun tube bore. Proper sub-projectile attitude and petal discard, with associated centering band functioning, upon shot ejection have been shown to be determining factors in projectile flight.<sup>8</sup>

It is emphasized that the results of the firings discussed in this report apply only to M392-type APDS projectiles and that it is not correct to interpret these results relative to full bore diameter projectiles (e.g. HEAT, HEP, and HVAP).

---

<sup>8</sup>APG Firing Record No. P-82488, Product Improvement Test of Cartridge, 105mm, APDS-T, M392A2 (Mode of Failure), 29 August 1975.

# APDS-T PROJECTILE

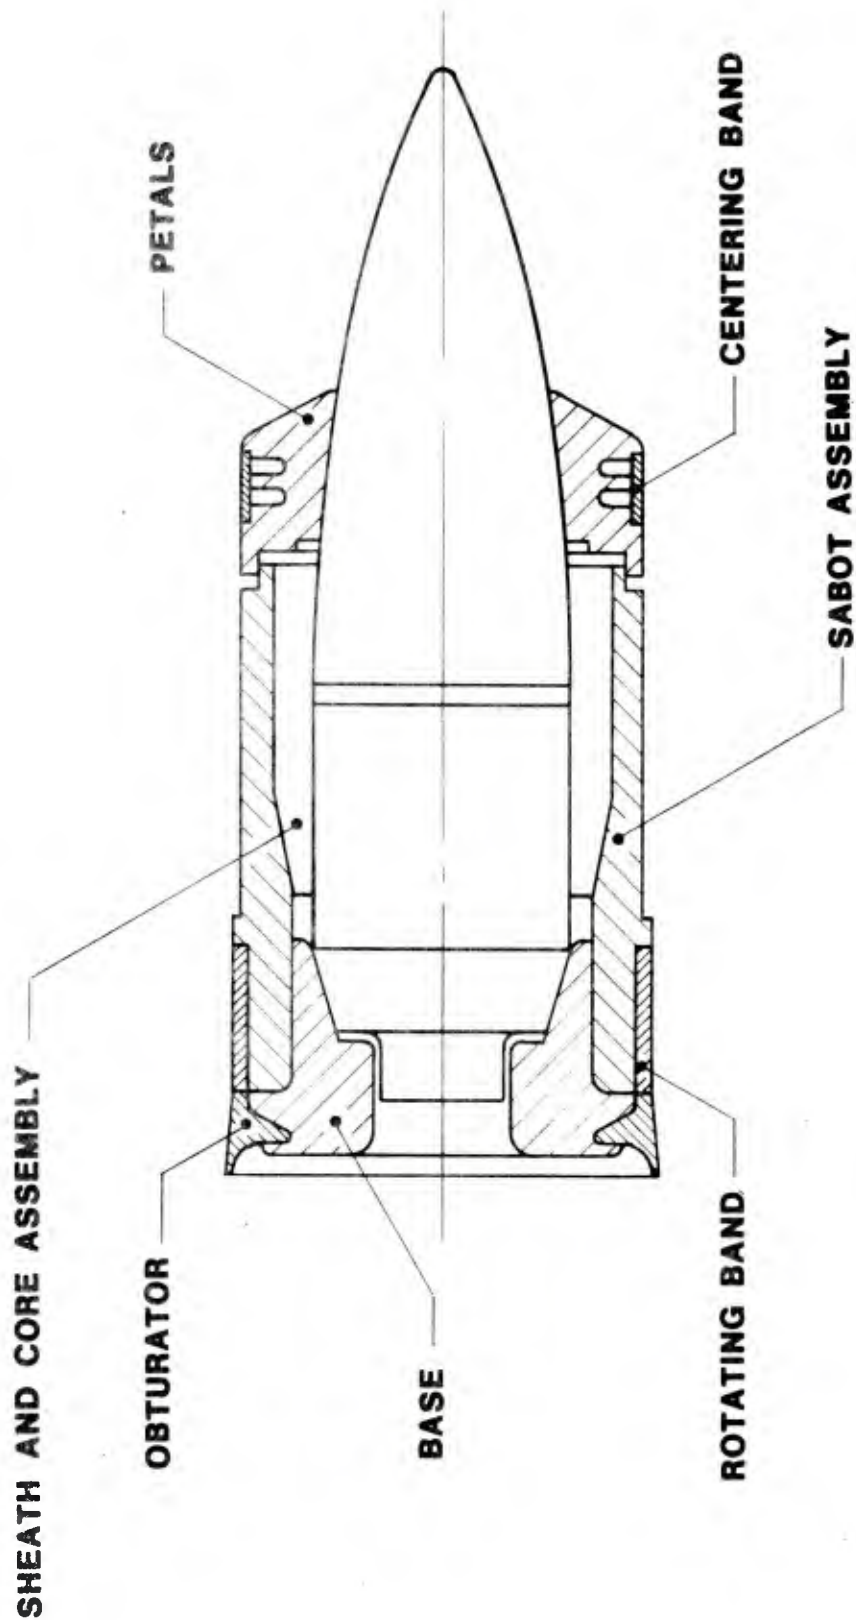


Figure 1. Sectional view of typical APDS-T projectile.

### Corrected Impact Data

Vertical target impacts recorded during test firing were corrected for a standard muzzle velocity of 4850 fps (1478.28 mps). Variations in local wind velocity and direction, and in air density, during firing were neglected. Figures 2, 3, and 4 are plots of the impact coordinates for each tube in the three replicates. Since this test addressed only dispersion characteristics, the centers of impact are shown as common for each of the three ten round groups for their respective tubes.

Corrections for standard muzzle velocity had minor effect on vertical impact standard deviations, reducing the value calculated for one tube in the third replicate by 0.01 mil.

For convenience in comparison, the following discussion of impact dispersion has been prepared in terms of circular error (CEP), with values given corresponding to the radius of a circle drawn at the center of impact and having an associated probability of including 50% of the impacts.<sup>9</sup> Table 3 shows circular errors associated with the pooled impact data for each of the three test tubes.

For reference, the desired dispersion for the M60-series tank, specified before type classification of either the M68 gun or the M60 tank, was horizontal and vertical standard deviations of 0.22 mils (corresponding to a circular probable error of 0.26 mils). These values have never been realized with any consistency; horizontal and

---

<sup>9</sup>This technique is discussed in Statistics Manual (E.L.Crow, F.A.Davies, and M.W. Maxfield, Dover Publications, Inc., NY, 1960) with necessary approximations described in Chapter 26 of Handbook of Mathematical Functions (M.Abramowitz and I. A. Stegun, National Bureau of Standards, GPO, June 1964).

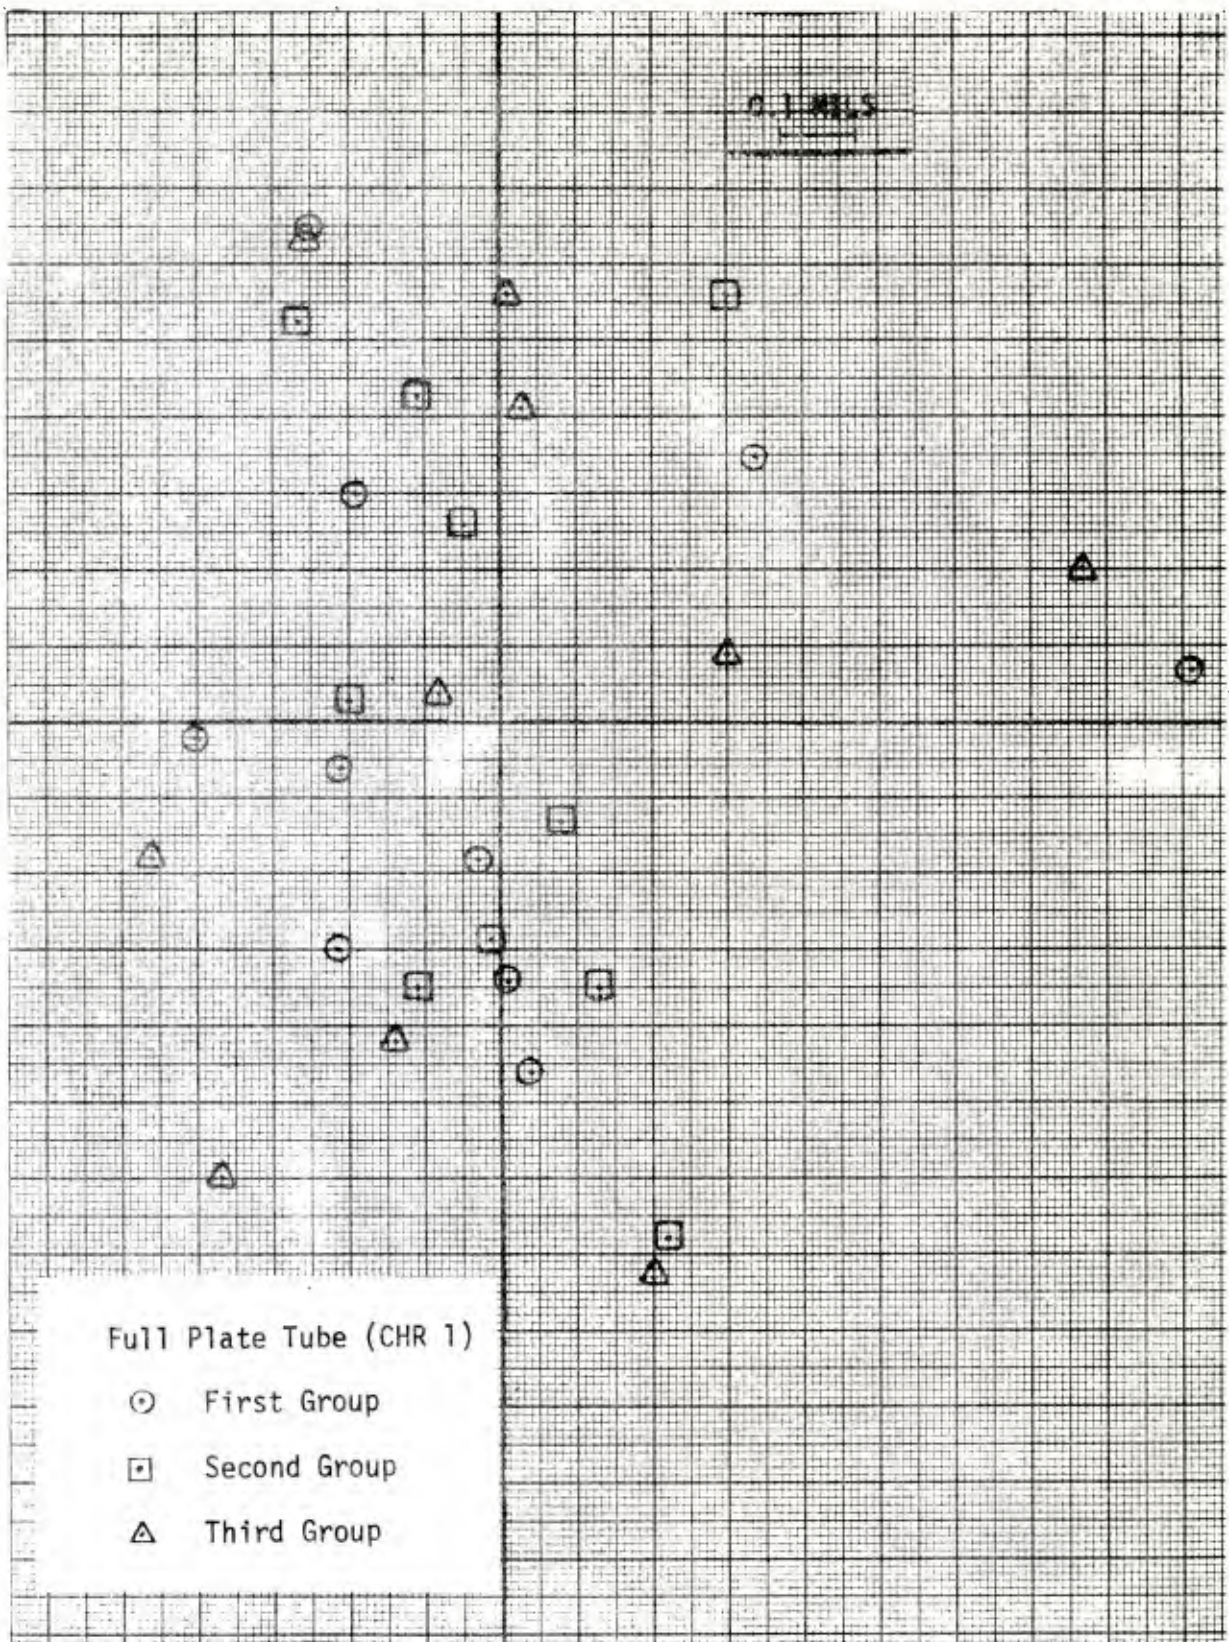


Figure 2. Target impacts--full length plated tube.

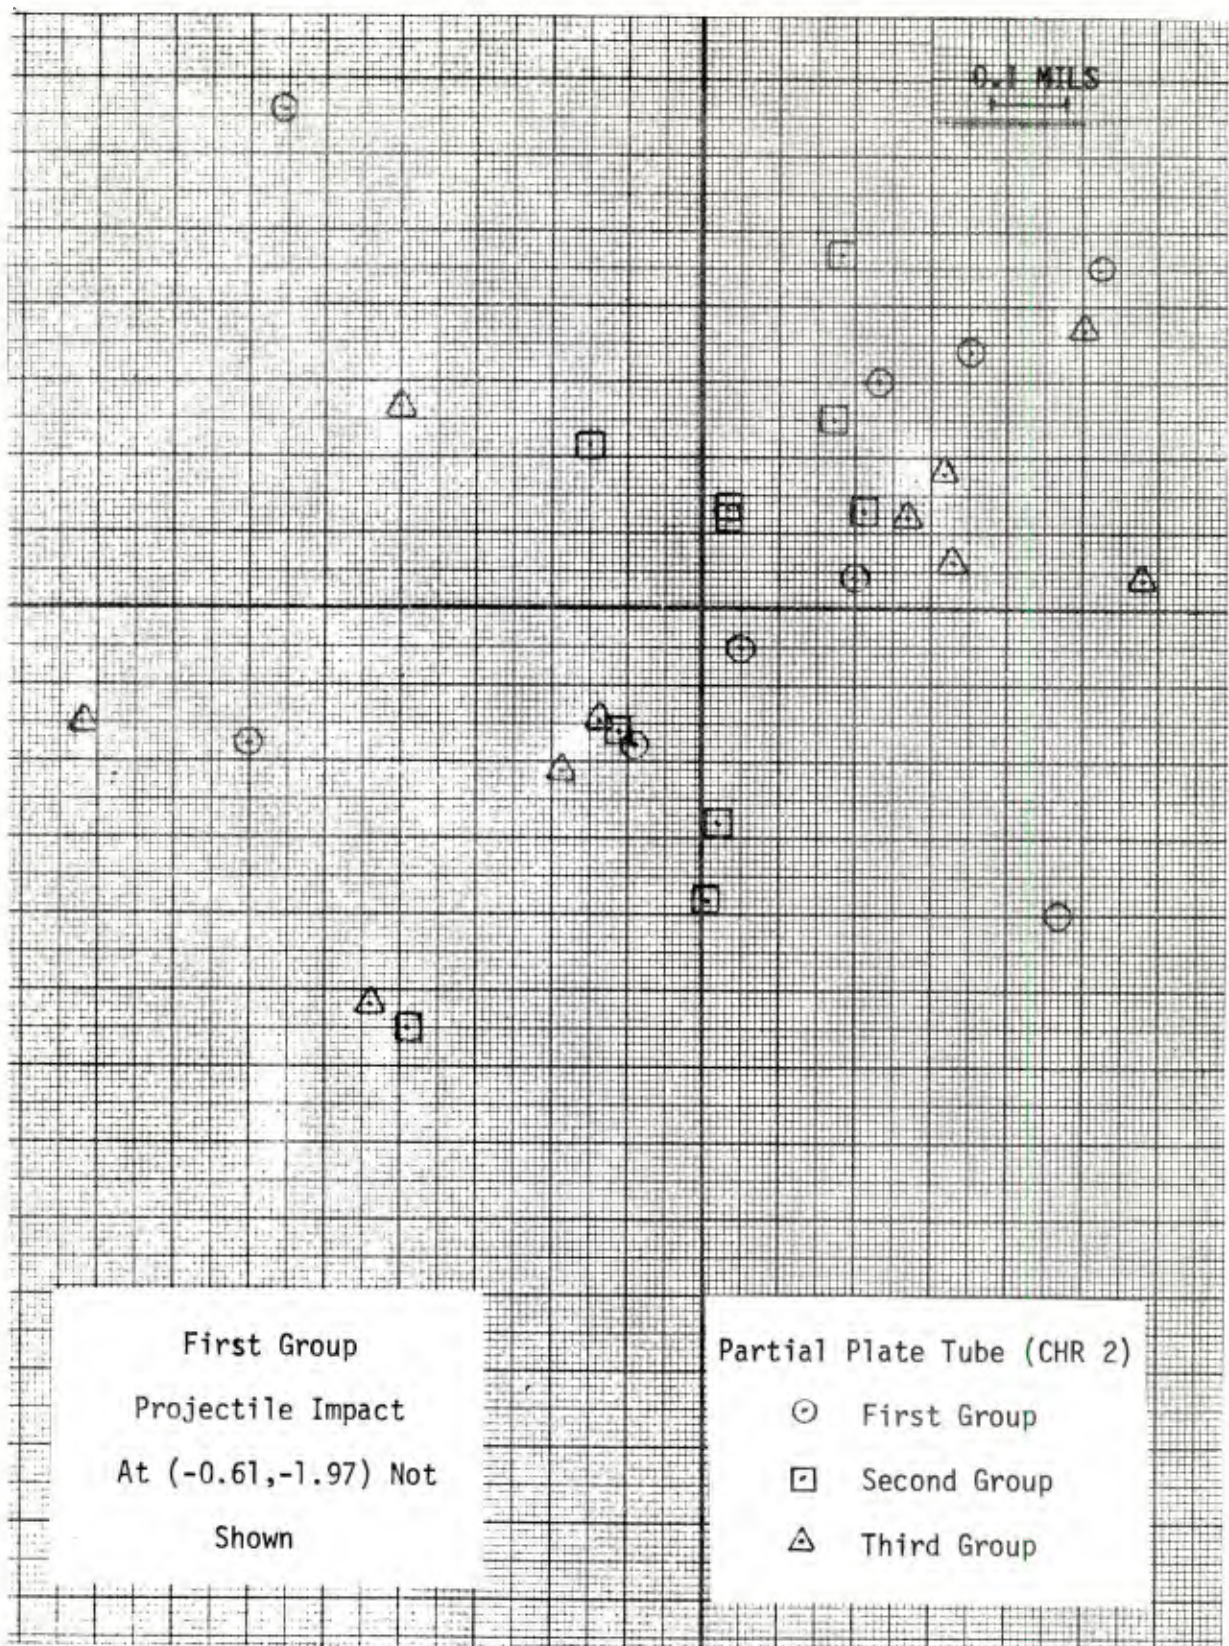


Figure 3. Target impacts--partial length plated tube.

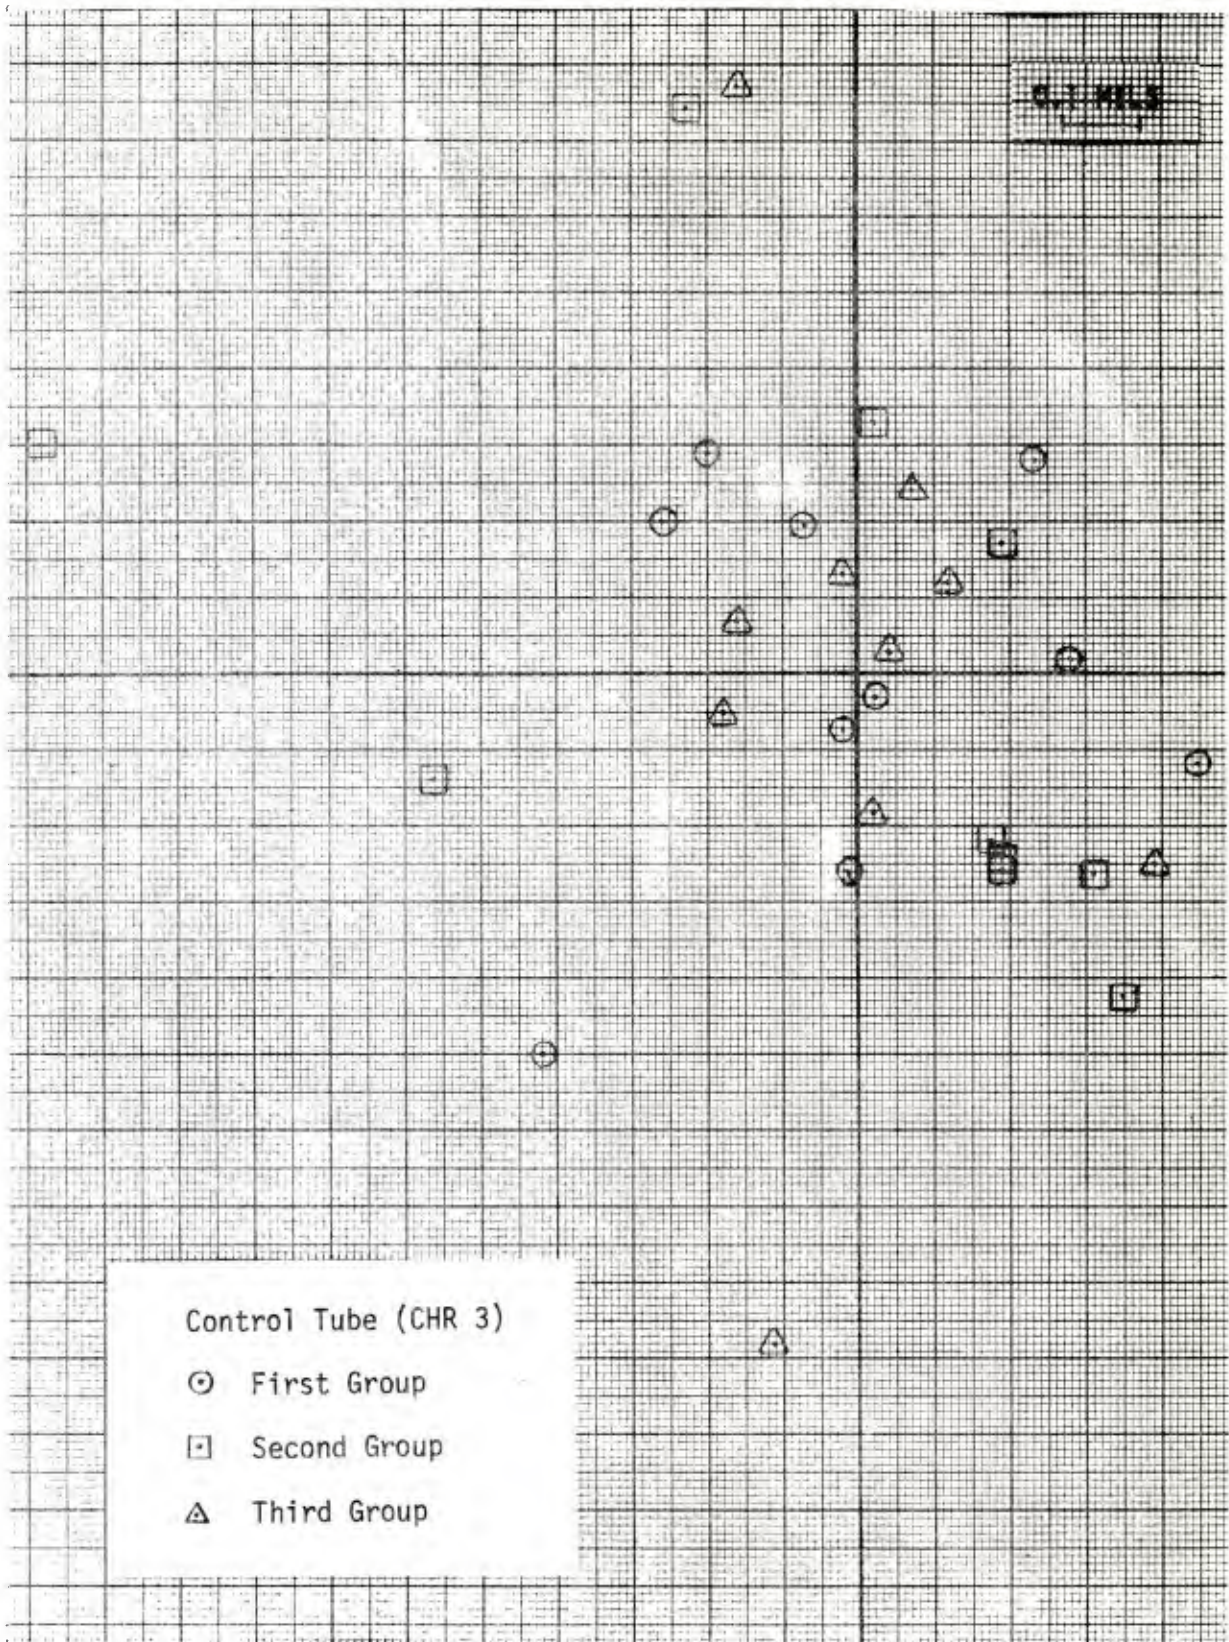


Figure 4. Target impacts--unplated tube.



vertical standard deviations from 563 occasions of M392A2 acceptance tests pool to 0.30 X 0.33 mils, or a CEP of 0.37 mils.<sup>10</sup>

TABLE 3. CIRCULAR IMPACT ERRORS

|                             |           |
|-----------------------------|-----------|
| CHR 1 (Full Plate)          | 0.42 MILS |
| CHR 2 (Partial Plate)       | .54       |
| CHR 3 (Unplated)            | .38       |
| Ammunition Acceptance Tests | .37       |

#### Film Data

Two 35mm smear cameras, located at 22.5 and 50 feet (6.858 and 15.240 meters) from the tube muzzle and perpendicular to the line of flight, provided photographs of projectile functioning which were used to analyze the characteristics of each flight. A complete tabulation of the results of this analysis is in Appendix B. Figures 5 through 10 present representative smear camera photographs of several of the abnormal flight conditions noted in the analysis.

To alleviate the influence of variations in ammunition performance, the impact group for each tube was censored by removing the impacts of projectiles which showed various characteristics, and combinations of characteristics, indicating abnormal flight. The results of this censoring is detailed in Table 4. Improved performance was noted in one instance for the full length plated tube, in two instances for the partial length plated tube, and in all instances for the unplated tube.

---

<sup>10</sup>Data drawn from ammunition acceptance records at Aberdeen Proving Ground.



Figure 5. Centering band interference at 22.5 feet (6.858M) - full length plated tube.

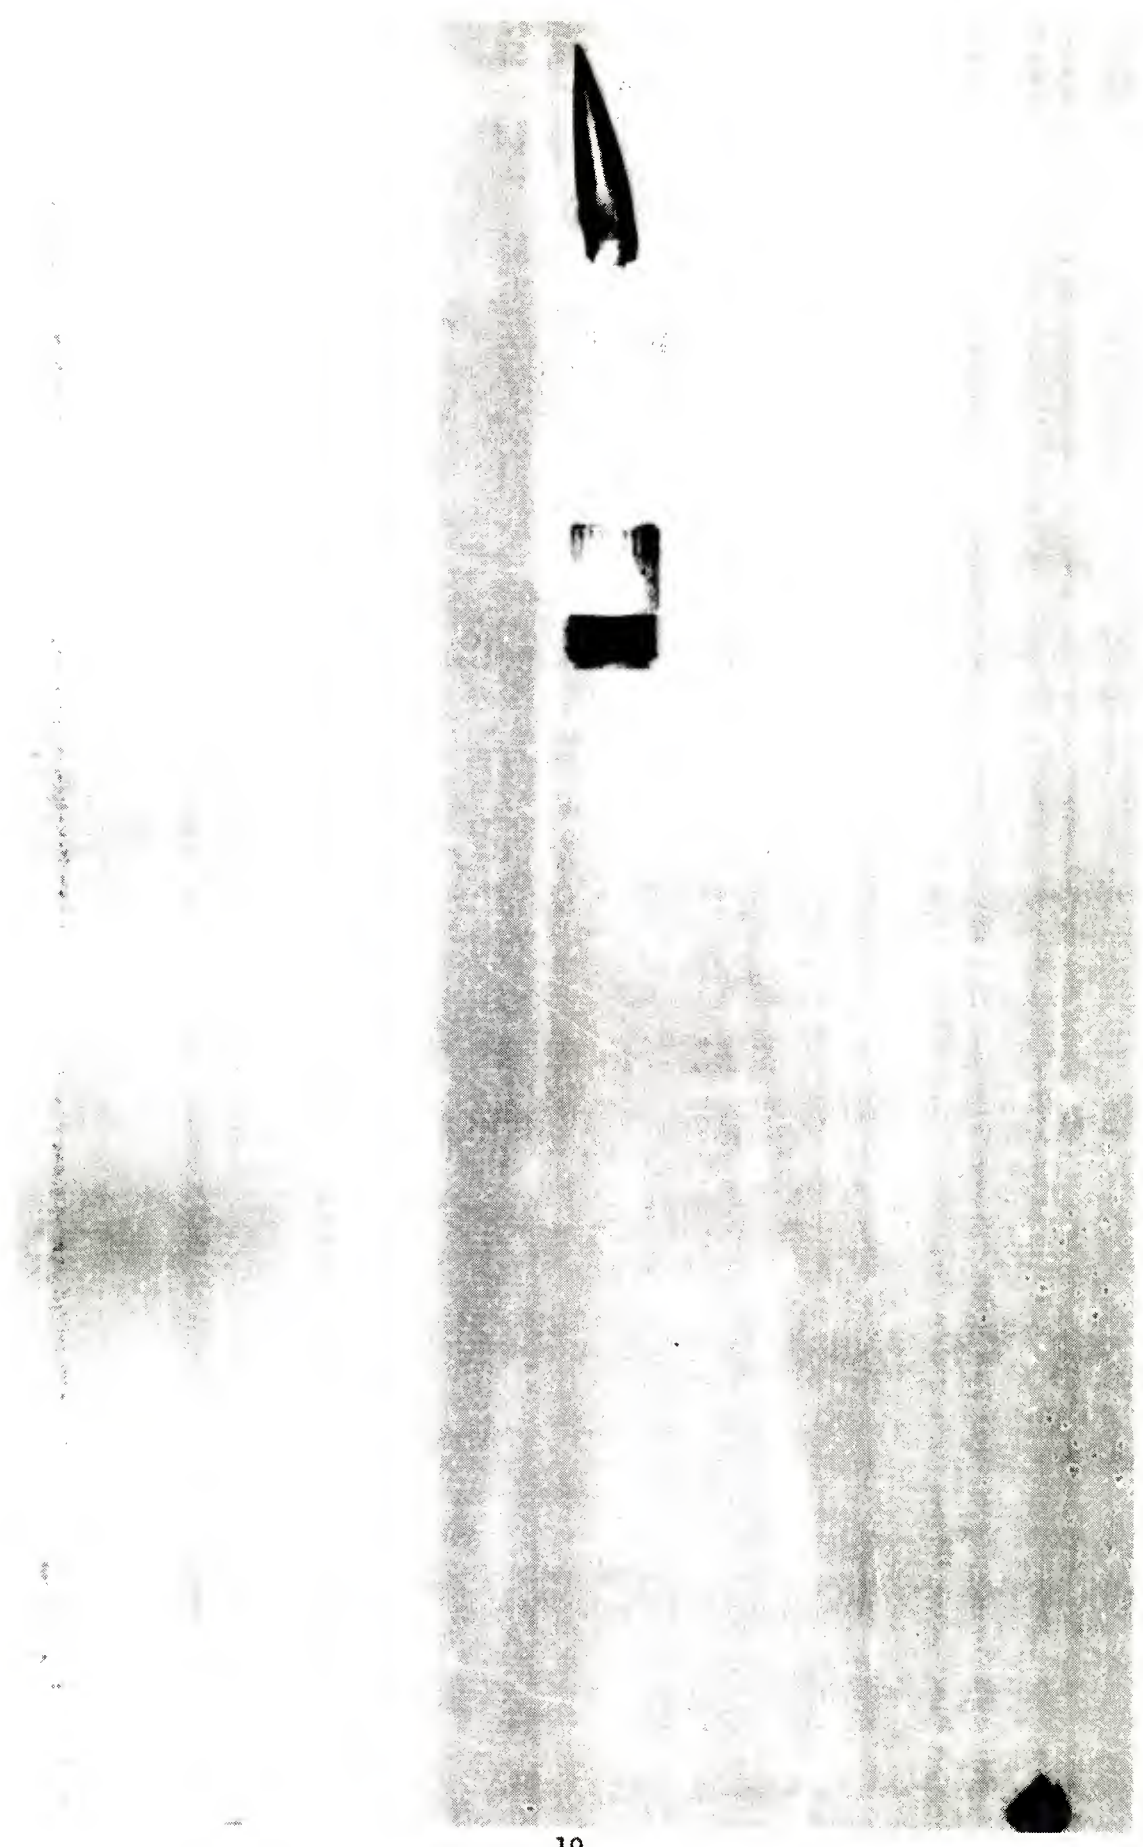


Figure 6. Subprojectile yaw over  $8^\circ$  at 50 feet (15.24M) - full length plated tube.

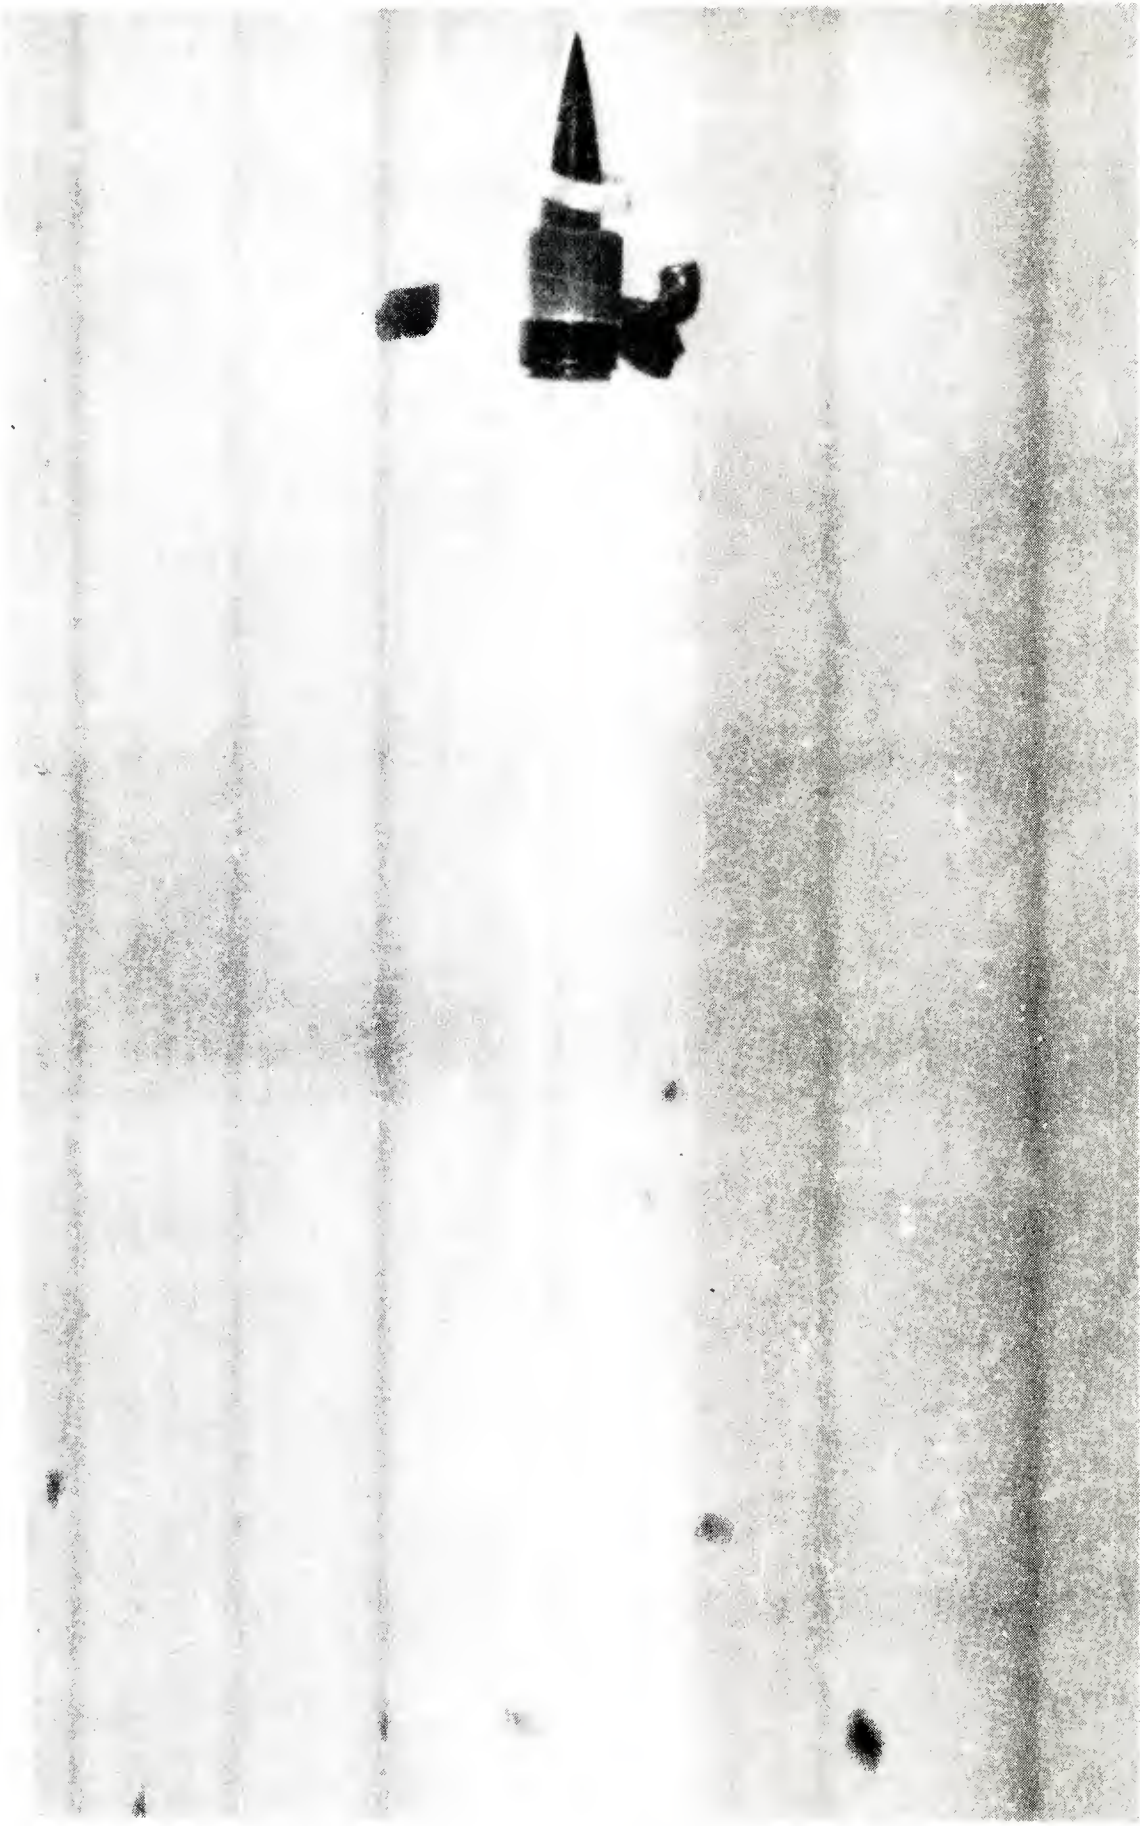


Figure 7. Centering band interference at 22.5 feet (6.858M) - partial length plated tube.

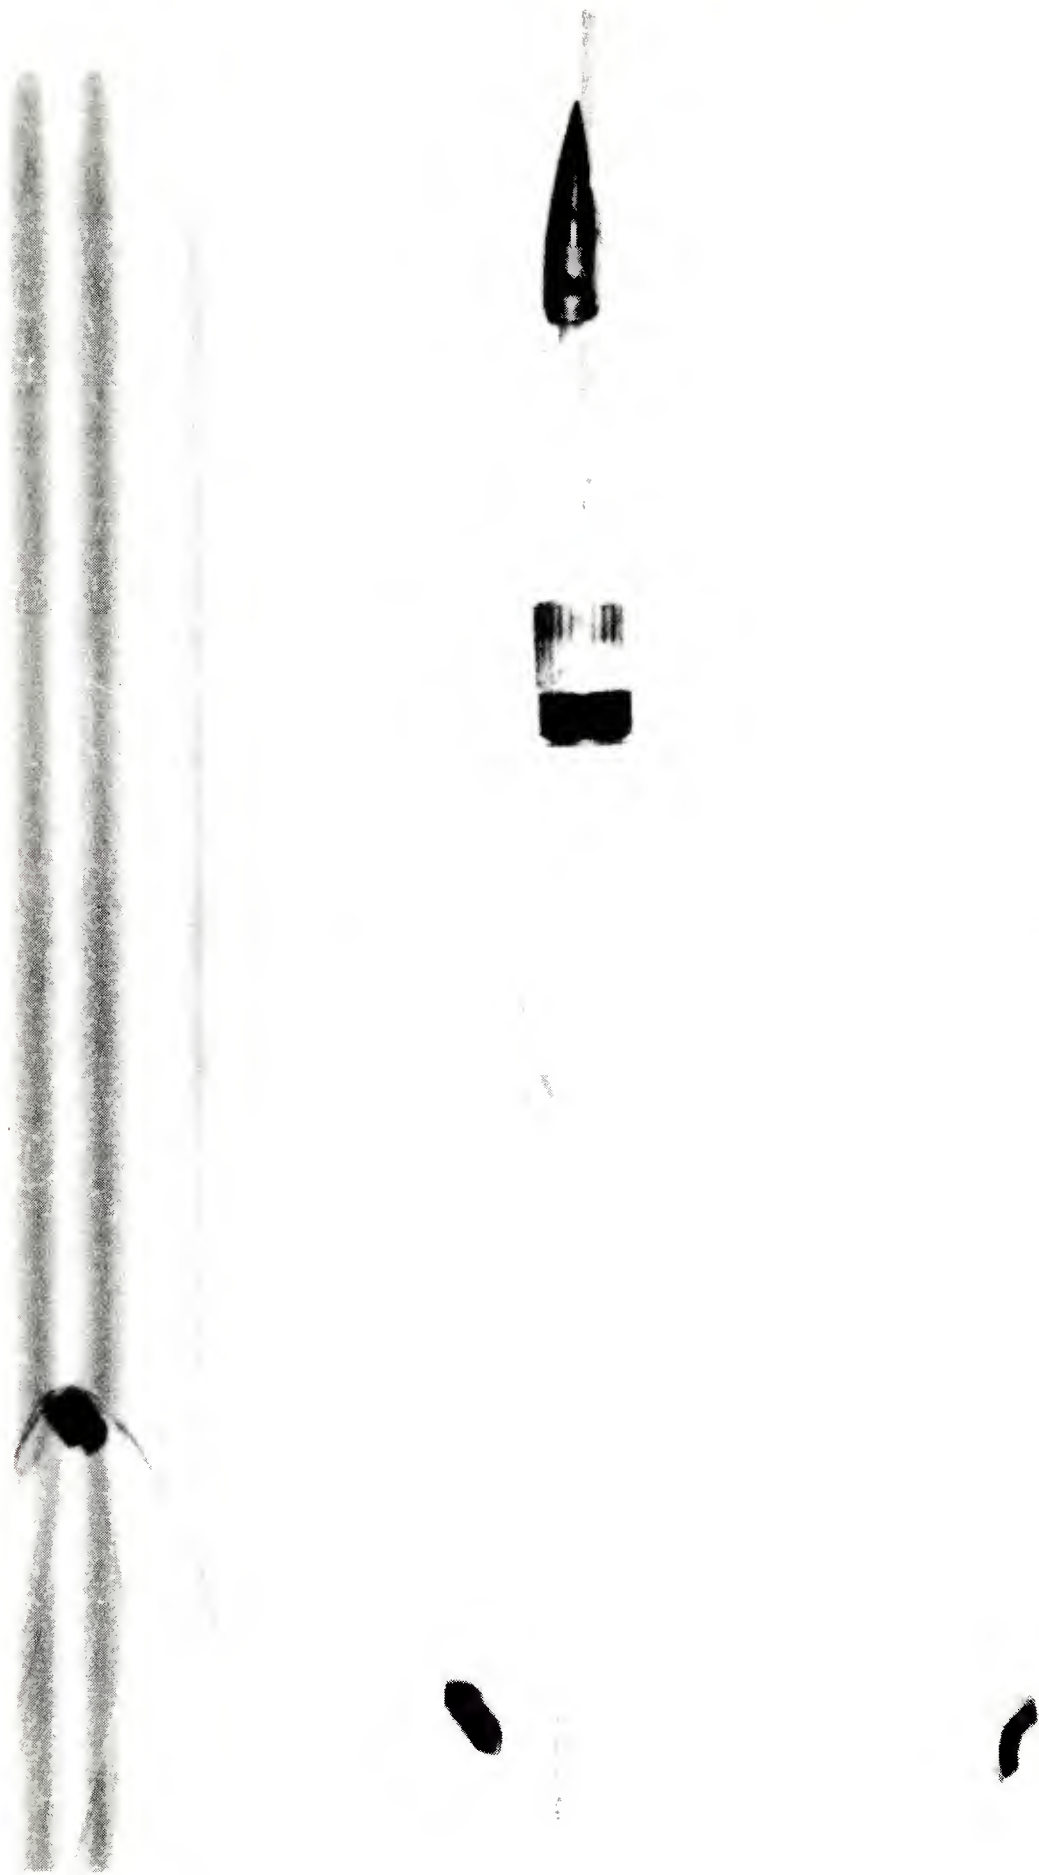


Figure 8. Late petal discard at 50 feet (15.24M) - partial length plated tube.



Figure 9. Centering band interference at 22.5 feet (6.858M) - unplated tube.




Figure 10. Yaw over 8° at 50 feet (15.24M) - unplatet tube.

TABLE 4. TARGET IMPACT DISPERSIONS WITH CENSORING OF ABNORMAL  
PROJECTILE FLIGHT IMPACTS

| <u>CHARACTERISTIC</u> <sup>1</sup> | <u>NUMBER CENSORED</u> |              |              | <u>CIRCULAR ERROR (MILS)</u> |              |              |
|------------------------------------|------------------------|--------------|--------------|------------------------------|--------------|--------------|
|                                    | <u>CHR 1</u>           | <u>CHR 2</u> | <u>CHR 3</u> | <u>CHR 1</u>                 | <u>CHR 2</u> | <u>CHR 3</u> |
| -                                  | -                      | -            | -            | 0.42                         | 0.54         | 0.38         |
| F                                  | 2                      | 0            | 2            | .42                          | .54          | .32          |
| J                                  | 0                      | 4            | 4            | .42                          | .61          | .30          |
| K                                  | 4                      | 7            | 2            | .39                          | .46          | .36          |
| F, K                               | 1                      | 0            | 2            | .43                          | .54          | .32          |
| J, K                               | 0                      | 3            | 4            | .42                          | .49          | .30          |
| F, J, K                            | 0                      | 0            | 2            | .42                          | .54          | .32          |

<sup>1</sup>F - Over 8° subprojectile yaw.

J - Late petal discard.

K - Centering band interference with subprojectile.

CHR 1 - Full length plated tube.

CHR 2 - Partial length plated tube.

CHR 3 - Unplated tube.



## CONCLUSIONS

The two chrome-plated tubes show a tendency towards greater dispersion. This tendency is emphasized when projectile flights with characteristics which have been shown to adversely influence impact dispersion are censored from the performance calculations. When this ammunition variable is alleviated, the relative performance of the unplated control tube consistently improves; this consistent improvement does not occur with the plated tubes.

The hypothesis of frictional characteristics of the bore surface affecting performance of APDS ammunition is supported by the evidence of higher muzzle velocities encountered with the plated tubes. The fact that higher muzzle velocities were measured in both tubes tends to indicate that the frictional influence is manifested within the first thirty inches of projectile travel.

Based on the severe chipping, flaking, and stripping encountered in the full length plated tube, its performance is considered unsatisfactory. The plating in the partial length plated tube remained intact and offers advantages in speed and ease of fabrication.

## RECOMMENDATIONS

1. The incorporation of wear resistant coatings to control levels of secondary bore wear in the 105mm M68 gun tube should be deferred until the interaction of APDS projectile functioning and bore coatings is fully established.

2. An exploratory development program, addressing the interaction of bore coatings and the APDS projectile, should be established.

3. The advantages of partial length plating over full length plating should be considered in other plating programs.

APPENDIX A  
STAR GAUGE AND BORESCOPE INSPECTIONS

The following borescope inspection report is taken from the APG letter report.<sup>11</sup>

105MM M68 TUBE CHR 1 AFTER FIRING 1 ROUND

"BORESCOPED: (Chrome plated between 21.60" from rear face of tube and muzzle.)

Light scratches, stains, and deposits throughout chamber, bore, and rifling. Seventeen lands at various times in the forcing cone 24.60" from rear face of tube have the chrome plating chipped off on the non-driving side. Chrome removed from edges of lands on both driving and non-driving sides at various times and distances throughout bore. Chrome flaked from breech one-third of all bore evacuator holes. Lands in muzzle .25" of tube have chrome chipped from both driving and non-driving edges."

105MM M68 TUBE CHR 1 AFTER FIRING 37 ROUNDS

"BORESCOPED: (Chrome plated between 21.60" from rear face tube and muzzle.)

Light scratches, stains, carbon and other deposits throughout chamber and bore. Lands in forcing cone 24.60" from rear face tube (RFT) have chrome chipped from non-driving side. Chrome chipped,

---

<sup>11</sup>USA TECOM Report No. APG-MT-4802.

flaked and stripped from lands at various times and distances throughout bore, more pronounced between 9:00 and 3:00 o'clock. Chrome flaked from edges of bore evacuator holes with light erosion in base metal. Lands in muzzle .25" of tube have chrome chipped from both driving and non-driving edges."

Star gauge measurements of the tube bore of each of the gun tubes, taken at the completion of test firings, are shown in Tables A1, A2, and A3.

TABLE A1. STAR GAUGE MEASUREMENTS AT COMPLETION OF  
TESTING--FULL LENGTH PLATED TUBE

| DISTANCE FROM<br>REAR FACE OF<br>TUBE (INCHES) | VERTICAL<br>LAND | VERTICAL<br>GROOVE | DISTANCE FROM<br>REAR FACE OF<br>TUBE (INCHES) | VERTICAL<br>LAND | VERTICAL<br>GROOVE |
|--|------------------|--------------------|--|------------------|--------------------|
| 25.25  | 0.001            | -0.001             | 59   | 0.000            | 0.001              |
| 25.5   | .000             | ↑                  | 60   | - .001           | ↑                  |
| 26   | .000             | ↑                  | 66.5   | ↑                | ↑                  |
| 27   | - .001           | ↑                  | 72.5   | ↑                | ↑                  |
| 28   | ↑                | ↑                  | 78.5   | ↓                | ↓                  |
| 29   | ↑                | ↑                  | 84.5   | ↓                | ↓                  |
| 30   | ↑                | ↑                  | 90.5   | - .001           | .001               |
| 31   | ↑                | ↑                  | 96.5   | .011             | .000               |
| 32   | ↑                | ↑                  | 102.5  | - .001           | ↑                  |
| 33   | ↑                | ↑                  | 108.5  | ↑                | ↑                  |
| 34   | ↑                | ↑                  | 114.5  | ↑                | ↑                  |
| 35   | ↑                | ↑                  | 120.5  | ↓                | ↑                  |
| 36   | ↑                | ↑                  | 126.5  | ↓                | ↑                  |
| 37   | ↑                | ↑                  | 132.5  | - .001           | ↑                  |
| 38   | ↑                | ↓                  | 138.5  | .008             | ↑                  |
| 39   | ↑                | - .001             | 144.5  | .006             | ↑                  |
| 40   | ↑                | .000               | 150.5  | .001             | ↑                  |
| 41   | ↑                | ↑                  | 156.5  | ↑                | ↓                  |
| 42   | ↑                | ↑                  | 162.5  | ↑                | ↓                  |
| 43   | ↑                | ↑                  | 168.5  | ↑                | ↓                  |
| 44   | ↑                | ↑                  | 174.5  | ↑                | .000               |
| 45   | ↑                | ↑                  | 180.5  | ↑                | .001               |
| 46   | ↑                | ↑                  | 186.5  | ↑                | ↑                  |
| 47   | ↑                | ↑                  | 192.5  | ↑                | ↑                  |
| 48   | ↑                | ↑                  | 198.5  | ↑                | ↓                  |
| 49   | ↑                | ↑                  | 200.5  | ↑                | ↓                  |
| 50   | ↑                | ↑                  | 202.5  | ↑                | ↓                  |
| 51   | ↑                | ↑                  | 204.5  | ↑                | .001               |
| 52   | ↑                | ↑                  | 205.5  | ↑                | - .001             |
| 53   | ↑                | ↓                  | 206.5  | ↑                | .000               |
| 54   | ↑                | ↓                  | 207.5  | ↓                | .000               |
| 55   | ↓                | .000               | 208.5  | ↓                | .000               |
| 56   | ↓                | .001               | 209.5  | .001             | .001               |
| 57   | - .001           | .001               | 210  | - .001           | - .002             |
| 58   | - .001           | .001               |  |                  |                    |

TABLE A2. STAR GAUGE MEASUREMENTS AT COMPLETION OF  
TESTING--PARTIAL LENGTH PLATED TUBE

| DISTANCE FROM<br>REAR FACE OF<br>TUBE (INCHES) | VERTICAL<br>LAND | VERTICAL<br>GROOVE | DISTANCE FROM<br>REAR FACE OF<br>TUBE (INCHES) | VERTICAL<br>LAND | VERTICAL<br>GROOVE |
|--|------------------|--------------------|--|------------------|--------------------|
| 25.25  | -0.004           | -0.004             | 59   | 0.001            | 0.002              |
| 25.5   | - .004           | - .004             | 60   | .001             |                    |
| 26   | - .004           | - .004             | 66.5   | .000             |                    |
| 27   | - .003           | - .004             | 72.5   |                  |                    |
| 28   | - .003           | - .003             | 78.5   |                  |                    |
| 29   | - .001           | - .002             | 84.5   |                  |                    |
| 30   |                  |                    | 90.5   | .000             |                    |
| 31   |                  |                    | 96.5   | .001             |                    |
| 32   |                  |                    | 102.5  |                  |                    |
| 33   | - .001           |                    | 108.5  |                  |                    |
| 34   | .000             |                    | 114.5  |                  |                    |
| 35   | .000             | - .002             | 120.5  |                  |                    |
| 36   | .000             | - .001             | 126.5  |                  |                    |
| 37   | .000             | - .001             | 132.5  |                  |                    |
| 38   | .001             | - .001             | 138.5  |                  |                    |
| 39   |                  | - .001             | 144.5  |                  |                    |
| 40   |                  | .000               | 150.5  | .001             |                    |
| 41   |                  |                    | 156.5  | .000             |                    |
| 42   |                  |                    | 162.5  | .000             |                    |
| 43   |                  |                    | 168.5  | .000             |                    |
| 44   |                  |                    | 174.5  | .000             |                    |
| 45   |                  |                    | 180.5  | .001             |                    |
| 46   |                  |                    | 186.5  |                  |                    |
| 47   |                  | .000               | 192.5  |                  |                    |
| 48   |                  | .001               | 198.5  |                  |                    |
| 49   | .001             |                    | 200.5  |                  |                    |
| 50   | .000             |                    | 202.5  | .001             |                    |
| 51   | .000             |                    | 204.5  | .002             |                    |
| 52   | .001             |                    | 205.5  |                  |                    |
| 53   | - .002           | .001               | 206.5  |                  |                    |
| 54   | .002             | .004               | 207.5  |                  |                    |
| 55   | .006             | .005               | 208.5  |                  |                    |
| 56   | .003             | .004               | 209.5  |                  |                    |
| 57   | .002             | .003               | 210  | .002             |                    |
| 58   | .001             | .002               |  |                  |                    |

TABLE A3. STAR GAUGE MEASUREMENTS AT COMPLETION OF TESTING--UNPLATED TUBE

| DISTANCE FROM REAR FACE OF TUBE (INCHES) | VERTICAL LAND | VERTICAL GROOVE | DISTANCE FROM REAR FACE OF TUBE (INCHES) | VERTICAL LAND | VERTICAL GROOVE |
|--|---------------|-----------------|--|---------------|-----------------|
| 25.25                                    | 0.005         | 0.002           | 59                                       | 0.001         | 0.000           |
| 25.5                                     | .003          | .002            | 60                                       | ↑             | .000            |
| 26                                       | .002          | .001            | 66.5                                     | ↑             | .001            |
| 27                                       | .002          | .001            | 72.5                                     | ↓             |                 |
| 28                                       | .002          | .001            | 78.5                                     | .001          | ↑               |
| 29                                       | .001          | .000            | 84.5                                     | .002          |                 |
| 30                                       | ↑             | ↑               | 90.5                                     | ↑             |                 |
| 31                                       |               |                 | 96.5                                     |               |                 |
| 32                                       | ↓             | ↓               | 102.5                                    | ↓             |                 |
| 33                                       |               |                 | 108.5                                    |               |                 |
| 34                                       |               |                 | 114.5                                    |               |                 |
| 35                                       |               |                 | 120.5                                    |               |                 |
| 36                                       |               |                 | 126.5                                    |               |                 |
| 37                                       |               |                 | 132.5                                    |               |                 |
| 38                                       |               |                 | 138.5                                    |               |                 |
| 39                                       |               |                 | 144.5                                    |               |                 |
| 40                                       |               |                 | 150.5                                    |               |                 |
| 41                                       |               |                 | 156.5                                    | ↓             |                 |
| 42                                       |               |                 | 162.5                                    | ↓             |                 |
| 43                                       |               |                 | 168.5                                    | .002          |                 |
| 44                                       |               |                 | 174.5                                    | .001          |                 |
| 45                                       |               |                 | 180.5                                    | ↑             |                 |
| 46                                       |               |                 | 186.5                                    | ↑             |                 |
| 47                                       |               |                 | 192.5                                    | ↓             |                 |
| 48                                       |               |                 | 198.5                                    | ↓             |                 |
| 49                                       |               |                 | 200.5                                    | .001          |                 |
| 50                                       |               |                 | 202.5                                    | .002          |                 |
| 51                                       |               |                 | 204.5                                    | ↑             |                 |
| 52                                       |               |                 | 205.5                                    | ↑             |                 |
| 53                                       |               |                 | 206.5                                    | ↓             |                 |
| 54                                       |               |                 | 207.5                                    | .002          | .001            |
| 55                                       |               |                 | 208.5                                    | .001          | .002            |
| 56                                       |               |                 | 209.5                                    | .001          | .002            |
| 57                                       | ↓             | ↓               | 210                                      | .001          | .000            |
| 58                                       | .001          | .000            |  |               |                 |

APPENDIX B  
PROJECTILE FLIGHT CHARACTERIZATIONS

Smear camera photographs were analyzed to identify flight characteristics of projectiles fired in the dispersion testing. Tables B1, B2, and B3 describe the results of this analysis.



TABLE B1. PROJECTILE FLIGHT CHARACTERISTICS--FULL LENGTH PLATED TUBE

| <u>ROUND</u> | <u>CHARACTERISTIC<sup>1</sup></u> |                 | <u>ROUND</u> | <u>CHARACTERISTIC</u> |                 |
|--------------|-----------------------------------|-----------------|--------------|-----------------------|-----------------|
|              | 22.5 FT                           | 50 FT           |              | 22.5 FT               | 50 FT           |
|              | <u>(6.858M)</u>                   | <u>(15.24M)</u> |              | <u>(6.858M)</u>       | <u>(15.24M)</u> |
| 3            | D, S                              | E               | 20           | D, S                  | D, S            |
| 4            | D, S                              | D, S            | 21           | D, S                  | F               |
| 5            | E                                 | D, S            | 22           | D, S                  | D, S            |
| 6            | D, S                              | D, S            | 23           | E                     | D, S            |
| 7            | E                                 | D, S            | 24           | D, S                  | D, S            |
| 8            | D, S                              | D, S            | 27           | K                     | D, S            |
| 9            | E                                 | D, S            | 28           | K                     | E               |
| 10           | A, D                              | E               | 29           | D, S                  | D, S            |
| 11           | D, S                              | D, S            | 30           | E                     | E               |
| 12           | D, S                              | D, S            | 31           | K                     | F               |
| 15           | D, S                              | D, S            | 32           | D, S                  | E               |
| 16           | E                                 | E               | 33           | D, S                  | E               |
| 17           | E                                 | D, S            | 34           | E                     | E               |
| 18           | D, S                              | D, S            | 35           | D, S                  | D, S            |
| 19           | E                                 | E               | 36           | K                     | E               |

<sup>1</sup>A - Subprojectile not centered in sabot.

C - Rotating band on sabot.

D - 0° to 4° subprojectile yaw.

E - 5° to 8° subprojectile yaw.

F - Over 8° subprojectile yaw.

S - Satisfactory.

J - Late petal discard.

K - Centering band

interference with  
subprojectile.

TABLE B2. PROJECTILE FLIGHT CHARACTERISTICS--PARTIAL LENGTH PLATED TUBE

| <u>ROUND</u> | <u>CHARACTERISTIC<sup>1</sup></u> |                                 | <u>ROUND</u> | <u>CHARACTERISTIC</u>             |                                 |
|--------------|-----------------------------------|---------------------------------|--------------|-----------------------------------|---------------------------------|
|              | <u>22.5 FT</u><br><u>(6.858M)</u> | <u>50 FT</u><br><u>(15.24M)</u> |              | <u>22.5 FT</u><br><u>(6.858M)</u> | <u>50 FT</u><br><u>(15.24M)</u> |
| 3            | D, S                              | D, S                            | 20           | D, S                              | D, S                            |
| 4            | K                                 | D, S                            | 21           | D, S                              | D, S                            |
| 5            | A                                 | D, S                            | 22           | K                                 | D, S                            |
| 6            | D, S                              | D, S                            | 23           | D, S                              | D, S                            |
| 7            | D, S                              | D, S                            | 24           | D, S                              | D, S                            |
| 8            | D, S                              | D, S                            | 27           | K                                 | D, S                            |
| 9            | D, S                              | D, S                            | 28           | D, S                              | D, S                            |
| 10           | D, S                              | D, S                            | 29           | D, S                              | D, S                            |
| 11           | J                                 | E, J                            | 30           | J, K                              | D, S                            |
| 12           | D, S                              | D, S                            | 31           | K                                 | D, S                            |
| 15           | D, S                              | D, S                            | 32           | D, S                              | D, S                            |
| 16           | D, S                              | D, S                            | 33           | D, S                              | D, S                            |
| 17           | D, S                              | D, S                            | 34           | D, S                              | D, S                            |
| 18           | D, S                              | D, S                            | 35           | J, K                              | E                               |
| 19           | D, S                              | D, S                            | 36           | J, K                              | D, J                            |

<sup>1</sup>A - Subprojectile not centered in sabot.

C - Rotating band on sabot.

D - 0° to 4° subprojectile yaw.

E - 5° to 8° subprojectile yaw.

F - Over 8° subprojectile yaw.

S - Satisfactory.

J - Late petal discard.

K - Centering band interference with subprojectile.

TABLE B3. PROJECTILE FLIGHT CHARACTERISTICS--UNPLATED TUBE

| <u>ROUND</u> | <u>CHARACTERISTIC<sup>1</sup></u> |                                 | <u>ROUND</u> | <u>CHARACTERISTIC</u>             |                                 |
|--------------|-----------------------------------|---------------------------------|--------------|-----------------------------------|---------------------------------|
|              | <u>22.5 FT</u><br><u>(6.858M)</u> | <u>50 FT</u><br><u>(15.24M)</u> |              | <u>22.5 FT</u><br><u>(6.858M)</u> | <u>50 FT</u><br><u>(15.24M)</u> |
| 3            | D, S                              | D, S                            | 20           | D, S                              | D, S                            |
| 4            | D, S                              | D, S                            | 21           | D, S                              | D, S                            |
| 5            | D, S                              | D, S                            | 22           | K                                 | E                               |
| 6            | D, S                              | D, S                            | 23           | D, S                              | D, S                            |
| 7            | D, S                              | D, S                            | 24           | J, K                              | E                               |
| 8            | D, S                              | D, S                            | 27           | D, S                              | D, S                            |
| 9            | D, S                              | D, S                            | 28           | K                                 | D, S                            |
| 10           | D, S                              | D, S                            | 29           | J, K                              | D, S                            |
| 11           | D, S                              | D, S                            | 30           | D, S                              | D, S                            |
| 12           | J, K                              | F                               | 31           | D, S                              | D, S                            |
| 15           | J, K                              | F                               | 32           | D, S                              | D, S                            |
| 16           | D, S                              | D, S                            | 33           | D, S                              | D, S                            |
| 17           | D, S                              | D, S                            | 34           | D, S                              | D, S                            |
| 18           | D, S                              | D, S                            | 35           | D, S                              | D, S                            |
| 19           | D, S                              | D, S                            | 36           | D, S                              | D, S                            |

<sup>1</sup>A - Subprojectile not centered  
in sabot.

C - Rotating band on sabot.

D - 0° to 4° subprojectile yaw.

E - 5° to 8° subprojectile yaw.

F - Over 8° subprojectile yaw.

S - Satisfactory.

J - Late petal discard.

K - Centering band interference  
with subprojectile.

## EXTERNAL DISTRIBUTION LIST

May 1976

1 copy to each

CDR  
US ARMY MAT & DEV READ. COMD  
ATTN: DRCRD  
DRCRD-TC  
DRCRD-W  
5001 EISENHOWER AVE  
ALEXANDRIA, VA 22304

OFC OF THE DIR. OF DEFENSE R&E  
ATTN: ASST DIRECTOR MATERIALS  
THE PENTAGON  
WASHINGTON, D.C. 20315

CDR  
US ARMY TANK-AUTMV COMD  
ATTN: AMDTA-UL  
AMSTA-RKM MAT LAB  
WARREN, MICHIGAN 48090

CDR  
PICATINNY ARSENAL  
ATTN: SARPA-TS-S  
SARPA-VP3 (PLASTICS  
TECH EVAL CEN)  
DOVER, NJ 07801

CDR  
FRANKFORD ARSENAL  
ATTN: SARFA  
PHILADELPHIA, PA 19137

DIRECTOR  
US ARMY BALLISTIC RSCH LABS  
ATTN: AMXBR-LB  
ABERDEEN PROVING GROUND  
MARYLAND 21005

CDR  
US ARMY RSCH OFC (DURHAM)  
BOX CM, DUKE STATION  
ATTN: RDRD-IPL  
DURHAM, NC 27706

CDR  
WEST POINT MIL ACADEMY  
ATTN: CHMN, MECH ENGR DEPT  
WEST POINT, NY 10996

CDR  
US ARMY ARMT COMD  
ATTN: AMSAR-PPW-IR  
AMSAR-RD  
AMSAR-RDG  
ROCK ISLAND, IL 61201

CDR  
US ARMY ARMT COMD  
FLD SVC DIV  
ARMCOM ARMT SYS OFC  
ATTN: AMSAR-ASF  
ROCK ISLAND, IL 61201

CDR  
US ARMY ELCT COMD  
FT MONMOUTH, NJ 07703

CDR  
REDSTONE ARSENAL  
ATTN: AMSMI-RRS  
AMSMI-RSM  
ALABAMA 35809

CDR  
ROCK ISLAND ARSENAL  
ATTN: SARRI-RDD  
ROCK ISLAND, IL 61202

CDR  
US ARMY FGN SCIENCE & TECH CEN  
ATTN: AMXST-SD  
220 7TH STREET N.E.  
CHARLOTTESVILLE, VA 22901

DIRECTOR  
US ARMY PDN EQ. AGENCY  
ATTN: AMXPE-MT  
ROCK ISLAND, IL 61201

CDR  
HQ, US ARMY AVN SCH  
ATTN: OFC OF THE LIBRARIAN  
FT RUCKER, ALABAMA 36362

EXTERNAL DISTRIBUTION LIST (Cont)

1 copy to each

CDR  
US NAVAL WPNS LAB  
CHIEF, MAT SCIENCE DIV  
ATTN: MR. D. MALYEVAC  
DAHLGREN, VA 22448

DIRECTOR  
NAVAL RSCH LAB  
ATTN: DIR. MECH DIV  
WASHINGTON, D.C. 20375

DIRECTOR  
NAVAL RSCH LAB  
CODE 26-27 (DOCU LIB.)  
WASHINGTON, D.C. 20375

NASA SCIENTIFIC & TECH INFO FAC  
PO BOX 8757, ATTN: ACQ BR  
BALTIMORE/WASHINGTON INTL AIRPORT  
MARYLAND 21240

DEFENSE METALS INFO CEN  
BATTELLE INSTITUTE  
505 KING AVE  
COLUMBUS, OHIO 43201

MANUEL E. PRADO / G. STISSER  
LAWRENCE LIVERMORE LAB  
PO BOX 808  
LIVERMORE, CA 94550

DR. ROBERT QUATTRONE  
CHIEF, MAT BR  
US ARMY R&S GROUP, EUR  
BOX 65, FPO N.Y. 09510

2 copies to each

CDR  
US ARMY MOB EQUIP RSCH & DEV COMD  
ATTN: TECH DOCU CEN  
FT BELVOIR, VA 22060

CDR  
US ARMY MAT RSCH AGCY  
ATTN: AMXMR - TECH INFO CEN  
WATERTOWN, MASS 02172

CDR  
WRIGHT-PATTERSON AFB  
ATTN: AFML/MXA  
OHIO 45433

CDR  
REDSTONE ARSENAL  
ATTN: DOCU & TECH INFO BR  
ALABAMA 35809

12 copies

CDR  
DEFENSE DOCU CEN  
ATTN: DDC-TCA  
CAMERON STATION  
ALEXANDRIA, VA 22314

NOTE: PLEASE NOTIFY CDR, WATERVLIET ARSENAL, ATTN: SARVV-RT-TP,  
WATERVLIET, N.Y. 12189, IF ANY CHANGE IS REQUIRED TO THE ABOVE.

WATERVLIET ARSENAL INTERNAL DISTRIBUTION LIST

May 1976

|   | <u>No. of Copies</u> |
|---|----------------------|
| COMMANDER                                     | 1                    |
| DIRECTOR, BENET WEAPONS LABORATORY            | 1                    |
| DIRECTOR, DEVELOPMENT ENGINEERING DIRECTORATE | 1                    |
| ATTN: RD-AT                                   | 1                    |
| RD-MR   | 1                    |
| RD-PE   | 1                    |
| RD-RM   | 1                    |
| RD-SE   | 1                    |
| RD-SP   | 1                    |
| DIRECTOR, ENGINEERING SUPPORT DIRECTORATE     | 1                    |
| DIRECTOR, RESEARCH DIRECTORATE                | 2                    |
| ATTN: RR-AM                                   | 1                    |
| RR-C  | 1                    |
| RR-ME   | 1                    |
| RR-PS   | 1                    |
| TECHNICAL LIBRARY                             | 5                    |
| TECHNICAL PUBLICATIONS & EDITING BRANCH       | 2                    |
| DIRECTOR, OPERATIONS DIRECTORATE              | 1                    |
| DIRECTOR, PROCUREMENT DIRECTORATE             | 1                    |
| DIRECTOR, PRODUCT ASSURANCE DIRECTORATE       | 1                    |
| PATENT ADVISORS                               | 1                    |