

AD-A041 510

PENNWALT CORP KING OF PRUSSIA PA RESEARCH AND DEVELO--ETC F/G 7/4
CRYSTAL STRUCTURE AND MAGNETIC STUDIES OF BIS (MU-DIBUTYLPHOSPH--ETC(U)
JUN 77 R CINI, P COLAMARINO, P L ORIOLI N00014-69-C-0122

UNCLASSIFIED

1 OF 1

AD
A041510



NL



END

DATE
FILMED

8-77

OFFICE OF NAVAL RESEARCH

Contract N00014-69-C-0000
NR356-408/7-30-70 742

TECHNICAL REPORT NO. 22

CRYSTAL STRUCTURE AND MAGNETIC STUDIES OF
BIS (μ -DIBUTYLPHOSPHINATO)COPPER(II)

by

R. Cini, P. Colamarino, P. L. Orioli, L. S. Smith,
P. R. Newman, H. D. Gillman, and P. Nannelli

Prepared for publication

Pennwalt Corporation
Research and Development Department
King of Prussia, Pennsylvania

June 1977

Reproduction in whole or in part is permitted for
any purpose of the United State Government

Approved for Public Release; Distribution Unlimited

ADA 041510

AD NO. 1
DDC FILE COPY

DDC
RECEIVED
JUL 12 1977

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) CRYSTAL STRUCTURE AND MAGNETIC STUDIES OF BIS(M-DIBUTYLPHOSPHINATO)COPPER(II). (mu)		5. TYPE OF REPORT & PERIOD COVERED Technical Report, No. 22
7. AUTHOR(s) R./Cini, P./Colamarino, P. L./Orioli, L. S./Smith P. R./Newman, H. D. Gillman, and P. Nannelli		6. PERFORMING ORG. REPORT NUMBER
5. PERFORMING ORGANIZATION NAME AND ADDRESS Pennwalt Corporation 900 First Avenue King of Prussia, Pa. 19406		8. CONTRACT OR GRANT NUMBER(s) N00014-69-C-0122
11. CONTROLLING OFFICE NAME AND ADDRESS Department of the Navy Office of Naval Research Arlington, Virginia 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) (12) 23p.		12. REPORT DATE June 1977
		13. NUMBER OF PAGES 19
		15. SECURITY CLASS. (of this report) UNCLASSIFIED
15a. DECLASSIFICATION/DOWNGRADING SCHEDULE		
16. DISTRIBUTION STATEMENT (of this Report) Available to the public from NTIS. No limitations on distribu- tion.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES None		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Coordination polymers Electron paramagnetic resonance Copper(II) Dibutylphosphinate Antiferromagnetic Poly(metal phosphinate) Structure		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The structure of $\text{Cu}[\text{OP}(\text{C}_4\text{H}_9)_2\text{O}]_2$ in the solid state has been determined by three-dimensional single-crystal x-ray techniques. The compound crystallizes in the triclinic space group P1 with two formula units in a cell of dimensions: $a = 12.245(6)$, $b = 9.863(5)$, $c = 9.819(5)$ Å; $\alpha = 101.18(4)$, $\beta = 105.78(5)$, $\gamma = 93.77(4)^\circ$; $V = 1110.7$ Å ³ , $d_c = d_m =$		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

404 871

Abstract

The structure of $\text{Cu}[\text{OP}(\text{C}_4\text{H}_9)_2\text{O}]_2$ in the solid state has been determined by three-dimensional single-crystal x-ray techniques. The compound crystallizes in the triclinic space group $\text{P}\bar{1}$ with two formula units in a cell of dimensions: $\underline{a} = 12.245(6)$, $\underline{b} = 9.863(5)$, $\underline{c} = 9.819(5)$ Å; $\underline{\alpha} = 101.18(4)$, $\underline{\beta} = 105.78(5)$, $\underline{\gamma} = 93.77(4)^\circ$; $V = 1110.7$ Å³, $d_c = d_m = 1.25$ g cm⁻³. The structure was solved by the heavy-atom technique, and least squares refinement gave an R factor of 0.061. The structure consists of polymeric chains of copper atoms linked by double phosphinate bridges. The coordination around each copper atom can be described as a very flattened tetrahedron. The g tensors for oriented single crystals were determined by ESR and range from 2.07 to 2.41, with the larger value in a direction nearly normal to a mean plane formed by the copper atoms and the ligands. The spin orbit coupling constant suggests considerable mixing of metal and ligand orbitals in this polymer.

Introduction

The poly(metal phosphinates), which are inorganic coordination polymers consisting of metal ions linked by phosphinate (OPO) bridges, have been extensively studied because of their potential in a variety of high temperature applications including coatings and grease thickeners.² Recently we have become interested in the magnetic properties of these unique one dimensional inorganic complexes and initiated an investigation of these properties. In this regard we studied the temperature dependent magnetic susceptibilities of a number of these materials and found that the OPO bridges provided a path for antiferromagnetic superexchange $J/K \sim 0-5K$.^{3,4} In addition, more extensive studies of some chromium phosphinates also indicated that disorder plays an important role in determining the magnetic properties of these polymers by limiting the range of spin correlation.³ In order to extend our understanding of this system further, we report here a single crystal study of $Cu[OP(C_4H_9)_2O]_2$ including its complete crystallographic structure and the orientation of the electronic $\vec{g}$ tensor relative to the atomic configuration.

Experimental Section

The preparation of $Cu[OP(C_4H_9)_2O]_2$ has previously been reported.⁵ Some crystals were obtained from dilute aqueous solutions, whereas other larger crystals were obtained from dilute ethanol solutions.

Crystal Structure Data Collection. The title compound crystallizes in the triclinic space group $P\bar{1}$ with two formula units in a cell with dimensions $[\lambda(\text{Mo-K}\alpha) = 0.7107 \text{ \AA}^\circ, \mu(\text{Mo-K}\alpha) = 11.40 \text{ cm}^{-1}]$: $a = 12.245(6)$, $b = 9.863(5)$, $c = 9.819(5) \text{ \AA}$; $\alpha = 101.18(4)$, $\beta = 105.78(5)$, $\gamma = 93.77(4)^\circ$; $V = 1110.7 \text{ \AA}^3$. The calculated density of 1.249 g/cm^3 agrees well with that of 1.253 g/cm^3 measured by flotation in potassium tetraiodomercurate. Intensity data were collected on a Philips automatic diffractometer with the $\omega - 2\theta$ scan technique, at a scan speed of $0.05^\circ/\text{sec}$ and a scan width of 1.20° in ω . Stationary-counter stationary-crystal background counts of 15 sec were taken at each end of the scan range. The 2462 reflections having $I > 2\sigma(I)$ were collected in the range $6 < 2\theta < 50^\circ$ and used for the structure determination and refinement. The standard deviation $\sigma(I)$ of the corrected intensity I was taken as: $\sigma(I) = [P + 0.25(B_1 + B_2)(T_p/T_b)^2 + (KI)^2]^{1/2}$ where P is the peak count, B_1 and B_2 are the background counts, and T_p and T_b are the count times on the peak and background, respectively. The factor K was found to be 0.02 by a least squares fit of three standard reflections monitored at regular intervals. Intensities were corrected for Lorentz-polarization effects; absorption effects were neglected.

Structure Solution and Refinement. The structure was solved by the heavy-atom technique with the use of Patterson and Fourier syntheses, which gave all the non-hydrogen atom posi-

tions. Two cycles of least squares with isotropic temperature factors for all the atoms, followed by two cycles with anisotropic temperature factors for Cu, P and O atoms reduced the R factor to 0.061. The function minimized was $\sum w (|F_o| - |F_c|)^2$ with weights taken as $w = 4F_o^2/\sigma^2(F_o^2)$. At this point a difference electron density synthesis showed 26 out of 36 hydrogen atoms. The positions of the other hydrogen atoms were calculated. Introduction of hydrogen atoms with the temperature factors of the carbon atoms to which they are attached, followed by two cycles of least squares, gave final values for R and R' factors of 0.050 and 0.053 respectively (R' is defined as $[\sum w (|F_o| - |F_c|)^2 / \sum w F_o^2]^{1/2}$). Atomic scattering factors were taken from Cromer and Waber⁶ for Cu, P, O, and C atoms and from Stewart, et al.,⁷ for H atoms. Cu and P scattering factors were corrected for the real and imaginary part of anomalous dispersion effects. All the calculations were performed with the use of the X-RAY 72 system of programs, adapted for the C11 10070 computer of the University of Florence. Final atomic parameters with their estimated standard deviations are listed in Table 1.

Electron Spin Resonance

Single crystals were selected after observation under cross polarizers to eliminate twinned samples. Alignment was accomplished by using x-ray precession photographs of the zero-level reflections (hk0) and (0kl). The aligned crystal was then fixed to the wall of a rectangular TE₁₀₂ cavity which was cooled to 77K and operated at 10 GHz. The magnitude of the resonant field was calibrated by inserting a small amount of diphenyl picryl hydrazyl (DPPH) in the cavity. The resonant magnetic fields as a function of magnet angle were measured for three orthogonal rotations. The resulting data for each rotation (see Fig. 1) were fit to the expression.

$$g^2 = \alpha + \beta \cos^2 \theta + \gamma \sin^2 \theta$$

with

$$\alpha = \frac{g_+^2 + g_-^2}{2} \quad \beta = \frac{g_+^2 - g_-^2}{2} \cos 2\theta_+ \quad \gamma = \frac{g_+^2 - g_-^2}{2} \sin 2\theta_+$$

where g_+ and g_- are the maximum and minimum g values occurring at θ_+ and θ_- for each rotation. The parameters α^i , β^i , and γ^i (i denotes the rotation axis) are then used to define a matrix $\overline{\overline{w}}$. The eigenvalues of the $\overline{\overline{w}}$ matrix are the squares of the principal values of the $\overrightarrow{g}$ tensor. In addition the eigenvectors are composed of the directional cosines of the principal axes of the $\overrightarrow{g}$ tensor relative to the fixed (laboratory) coordinates used to index the external magnetic field

orientation. The previous alignment of the crystal was then used to relate the orientation of the principal axes of the g tensor to the atomic coordination surrounding each Cu^{2+} ion.⁸

Magnetic Susceptibility

Approximately 11 mg of polycrystalline material was used for measurement of the magnetic susceptibility in a Faraday balance over the temperature range from $77\text{K} \leq T \leq 300\text{K}$. The details of the experimental apparatus are described elsewhere.⁹

Description of the Structure. The overall structure of bis-(dibutylphosphinato)copper(II) is similar to that of the analogous bis(diphenylphosphinato)lead(II),¹⁰ i.e., it consists of polymeric chains in which the phosphinate groups form double bridges between copper atoms (Figure 2). The endless chains wind around the crystallographic c axis. The coordination around the copper atom can be described as a very flattened tetrahedron with approximate D_{2d} symmetry (Figure 3). This type of coordination geometry is rather common in four-coordinate copper(II) compounds. The average Cu-O distance is $1.920(4)\text{\AA}$, a value in agreement with other Cu-O bond lengths in four-coordinate copper compounds. The Cu-Cu distance along the chain is $4.938(2)$. Bond lengths and angles in the phosphinate group are in agreement with the values found in bis(diphenylphosphinato)lead(II) (Table 2).

The single crystal x-ray studies of a few zinc phosphinates showed them all to consist of tetrahedral metal atoms linked by alternating single and triple phosphinate bridges.¹¹ Some cobalt phosphinates have been shown to be isomorphous with their zinc analogs,¹² and x-ray fiber studies have indicated that a beryllium phosphinate also has the single-triple bridged structure.¹³ This copper phosphinate is the first definitively characterized poly(metal phosphinate) with tetrahedral metal centers (albeit distorted) and double phosphinate bridging.

ESR and The g-Tensor

The x-ray precession photographs were used to relate the principal g values and orientation of the g-tensor to the atomic coordination of the Cu^{2+} ions as shown in Fig. 4. The largest g-value, 2.41, is found in a direction nearly in the bc plane of the crystal, approximately normal to a plane formed by completely flattening the tetrahedron of four oxygens surrounding the copper.

This g-tensor is consistent with those normally seen for Cu^{2+} in an approximate square planar ligand field. For Cu^{2+} in a tetragonal field the principal g values are given by:

$$g_{zz} = 2 - \frac{8\lambda}{\Delta_0} \quad g_{xx} = g_{yy} = 2 - \frac{2\lambda}{\Delta_1}$$

in which Δ_0 is the splitting between $d_{x^2-y^2}$ and d_{xy} and Δ_1 is the difference in energy between $d_{x^2-y^2}$ and the (degenerate) d_{xz} and d_{yz} orbitals. Thus the largest g value should occur along the z -axis or perpendicular to the square planar arrangement. If we assume Δ_0 is approximately equal to $\Delta = 13000 \text{ cm}^{-1}$ (estimated from absorption spectra), we calculate a value of $\lambda = -500 \pm 100 \text{ cm}^{-1}$ (with the variation due to anisotropy). This is somewhat less than the free ion value of -830 cm^{-1} and indicates significant mixing of metal and ligand orbitals.

ESR - Linewidth

The resonance line was a single-well resolved absorption at all temperatures in the range $1.1\text{K} \leq T \leq 300\text{K}$. The linewidth and g value are both anisotropic but nearly temperature independent. Fig. 5 shows the range of linewidth anisotropy for a typical rotation. The angular dependence is reminiscent of magnetic dipolar interaction with functional dependence on angle given by $(3 \cos^2\theta - 1)^2$ in three dimensions and $(3 \cos^2\theta - 1)^{4/3}$ in one dimension. The solid and dash lines show the best fits of these functions to the data. The approximate agreement and the linear character to the crystal structure suggest the possibility of one-dimensional magnetic dipolar interactions competing with an (isotropic) exchange mechanism.

Magnetic Susceptibility

The high temperature magnetic susceptibility is Curie like with $C = 0.485(1)$. The g value of $\chi_{\text{susc}} = 2.18(1)$ derived from the Curie constant compares well with the geometric average of the ESR g values.

Acknowledgement. We thank Prof. P. Zanazzi for the use of the diffractometer at the Istituto di Mineralogia, University of Perugia. We also thank Profs. A. J. Heeger and A. F. Garito and Dr. B. P. Block for discussions. The work was supported at Pennwalt in part by the Office of Naval Research and at the University of Pennsylvania by NSF-MRL grant No. DMR76-00678.

Supplementary Material Available. A listing of structure factor amplitudes will appear following these pages in the microfilm edition of this volume of the journal. Photocopies of the supplementary material from this paper only or microfiche (105 x 148 mm, 24x reduction, negatives) containing all of the supplementary material for the papers in this issue may be obtained from the Journals Department, American Chemical Society, 1155 16th St., N.W., Washington, D.C. 20036. Remit check or money order for \$0.00 for photocopy or \$2.50 for microfiche, referring to code number AIC000000.

Figure Captions

- Figure 1. The measured g values as a function of magnet angle for three orthogonal rotations.
- Figure 2. ORTEP drawing showing the polymeric chain of bis(dibutylphosphinato)copper(II).
- Figure 3. ORTEP drawing of the bis(dibutylphosphinato)-copper(II) moiety. The numbering scheme is the same as that used in the tables. Superscripts 1 and 11 refer respectively to atoms related through the centers of symmetry at 0,0,0 and 0,0,1/2.
- Figure 4. The orientation of the principal g values.
- Figure 5. Linewidth variation as a function of angle of rotation.

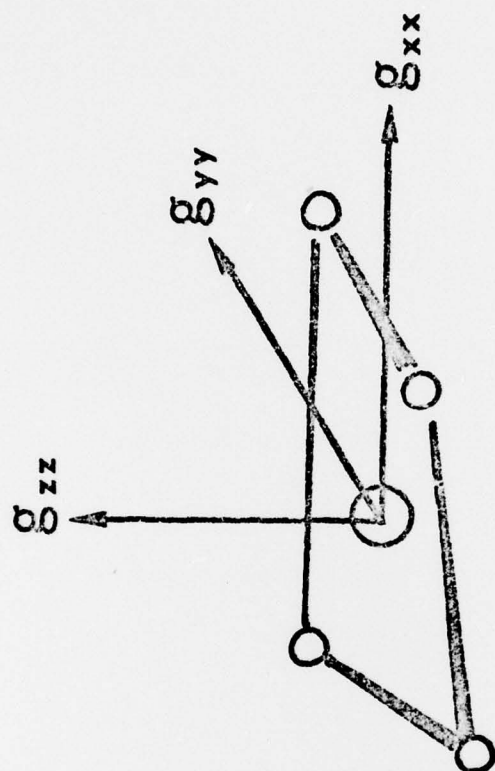


FIG. 1

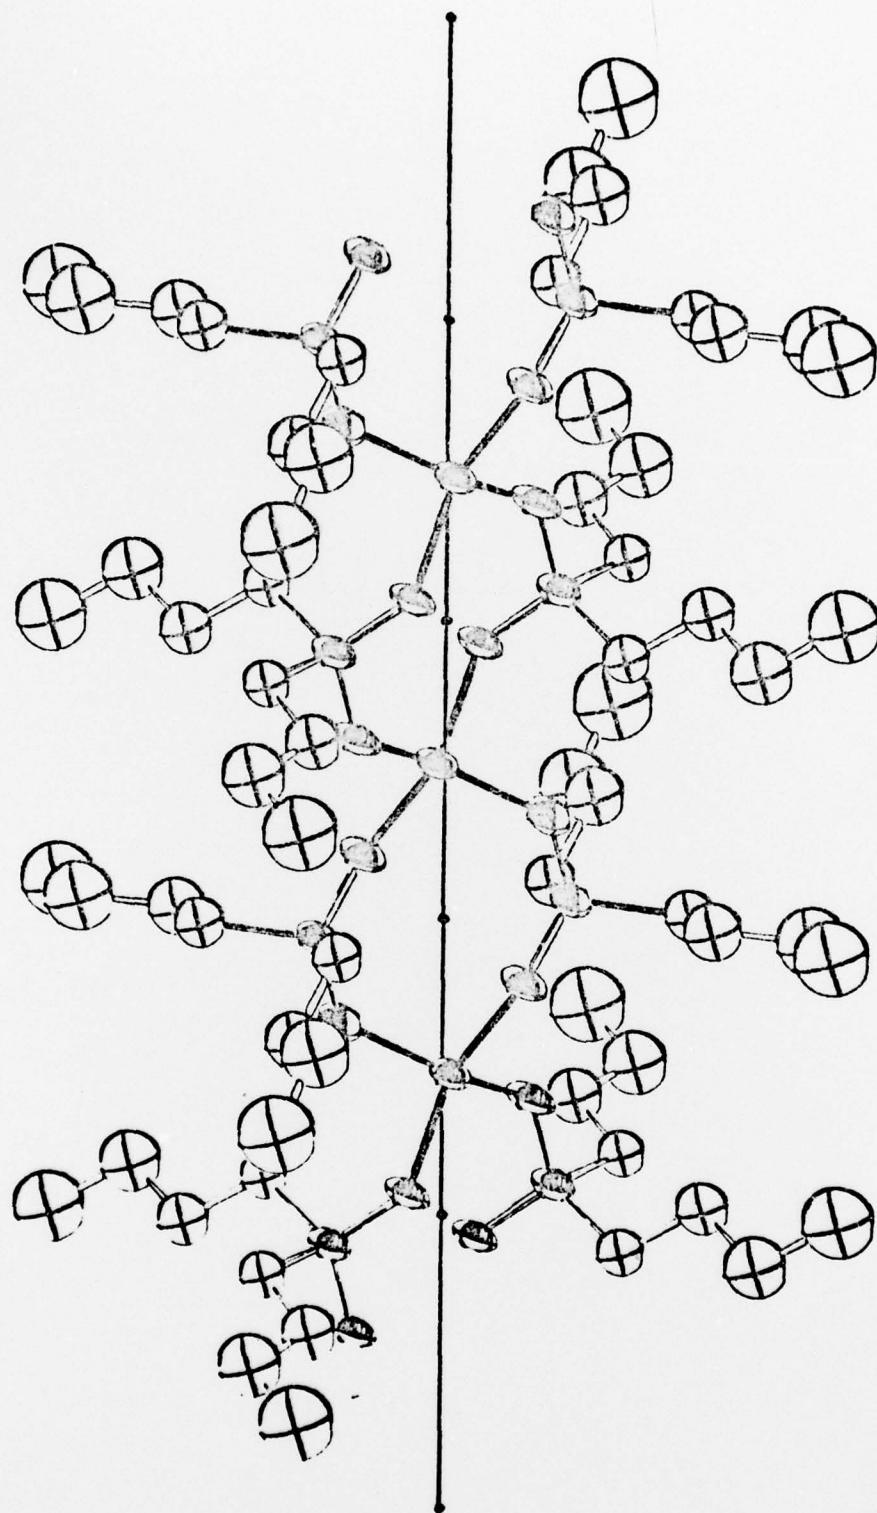


FIG. 2

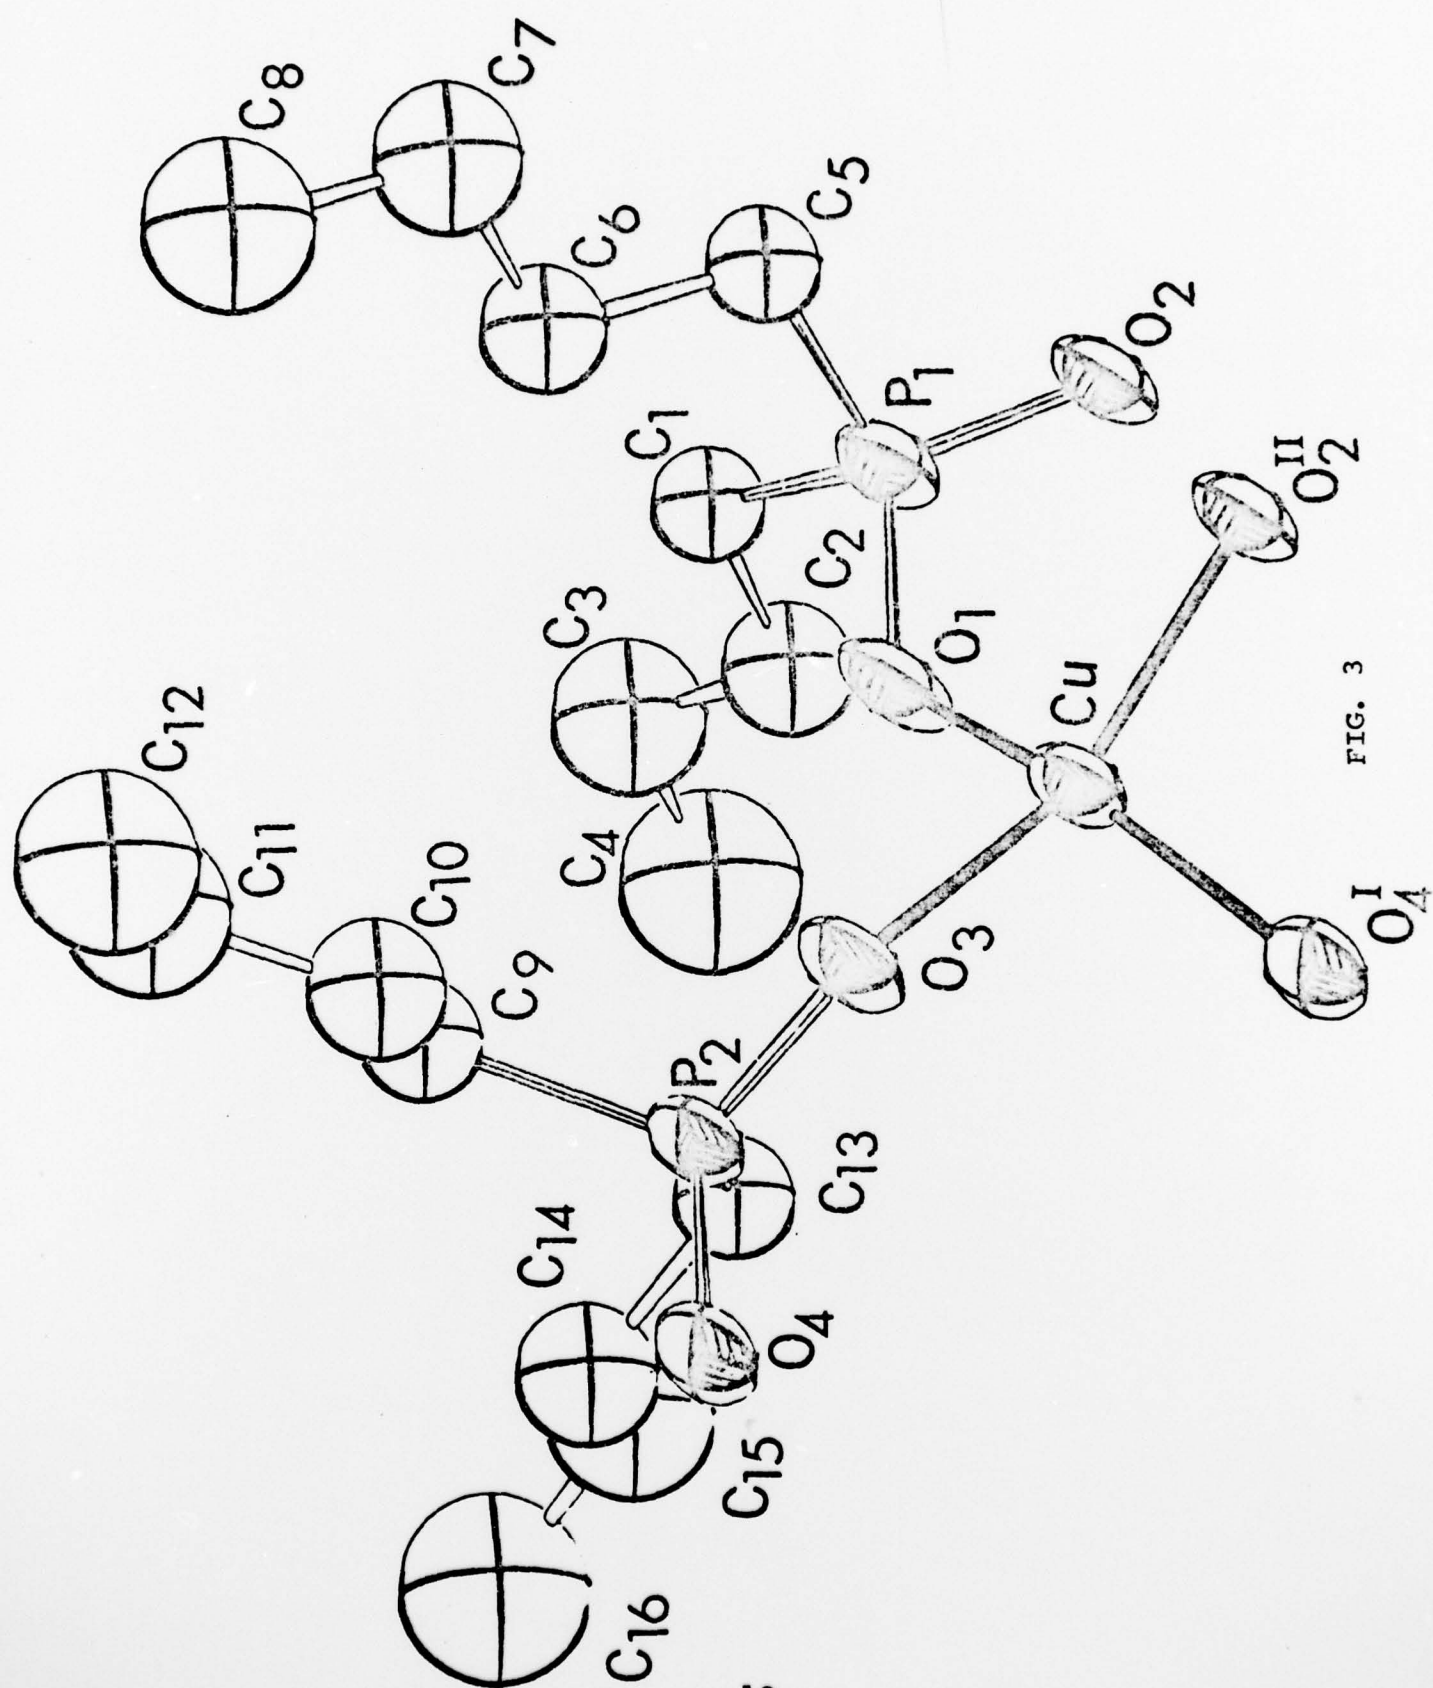


FIG. 3

FIG. 4


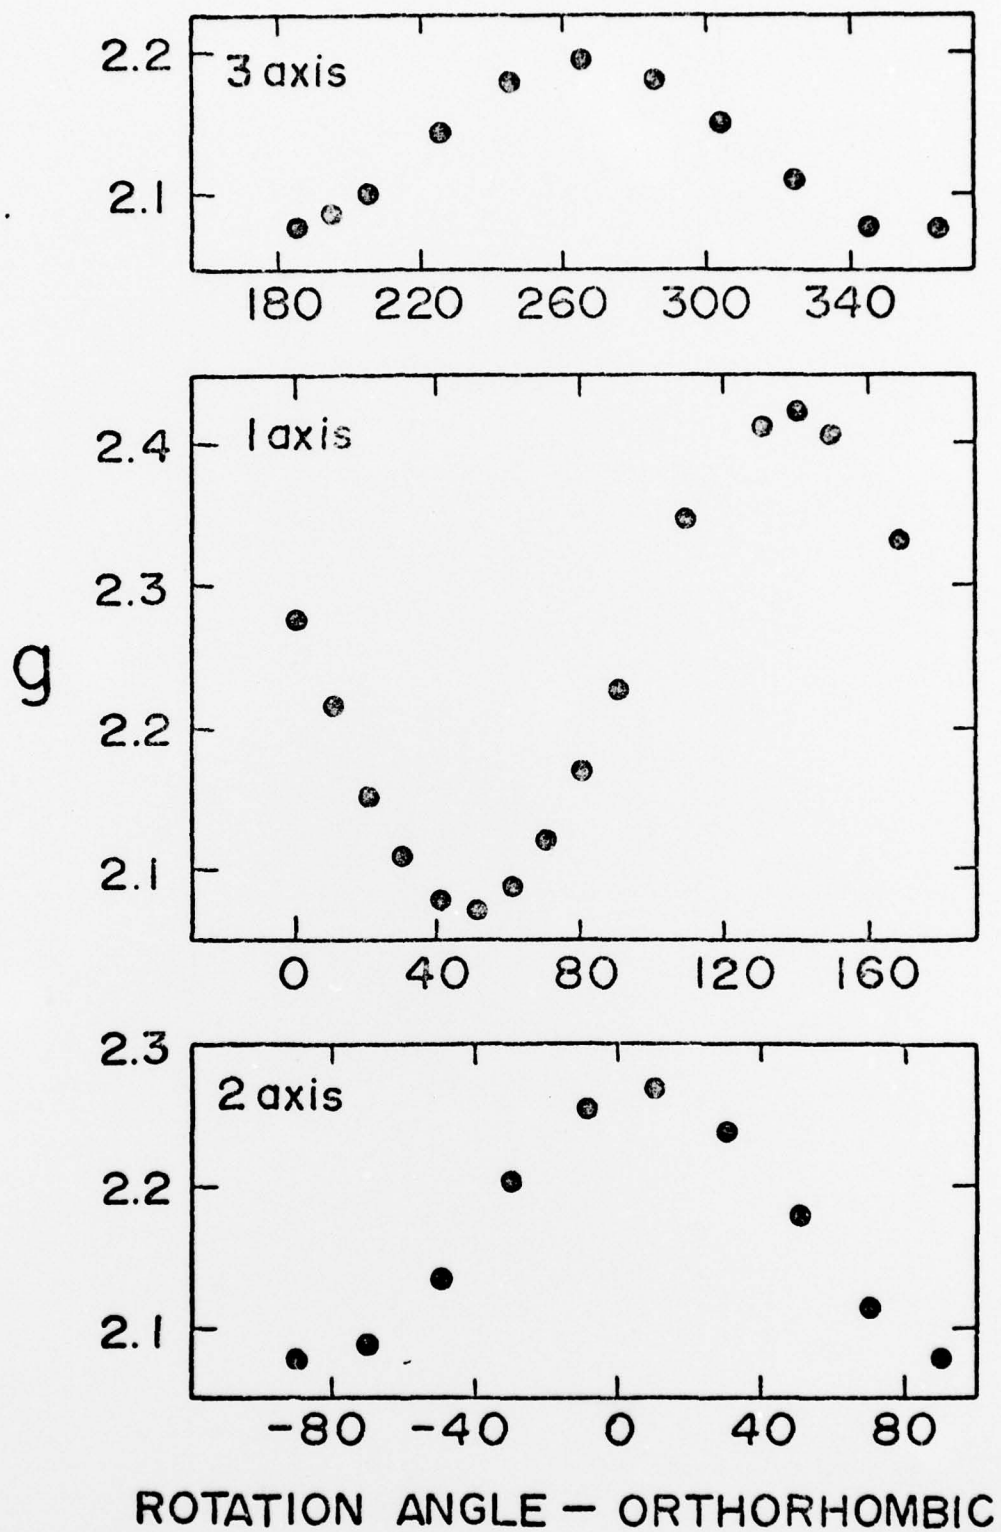


FIG. 5

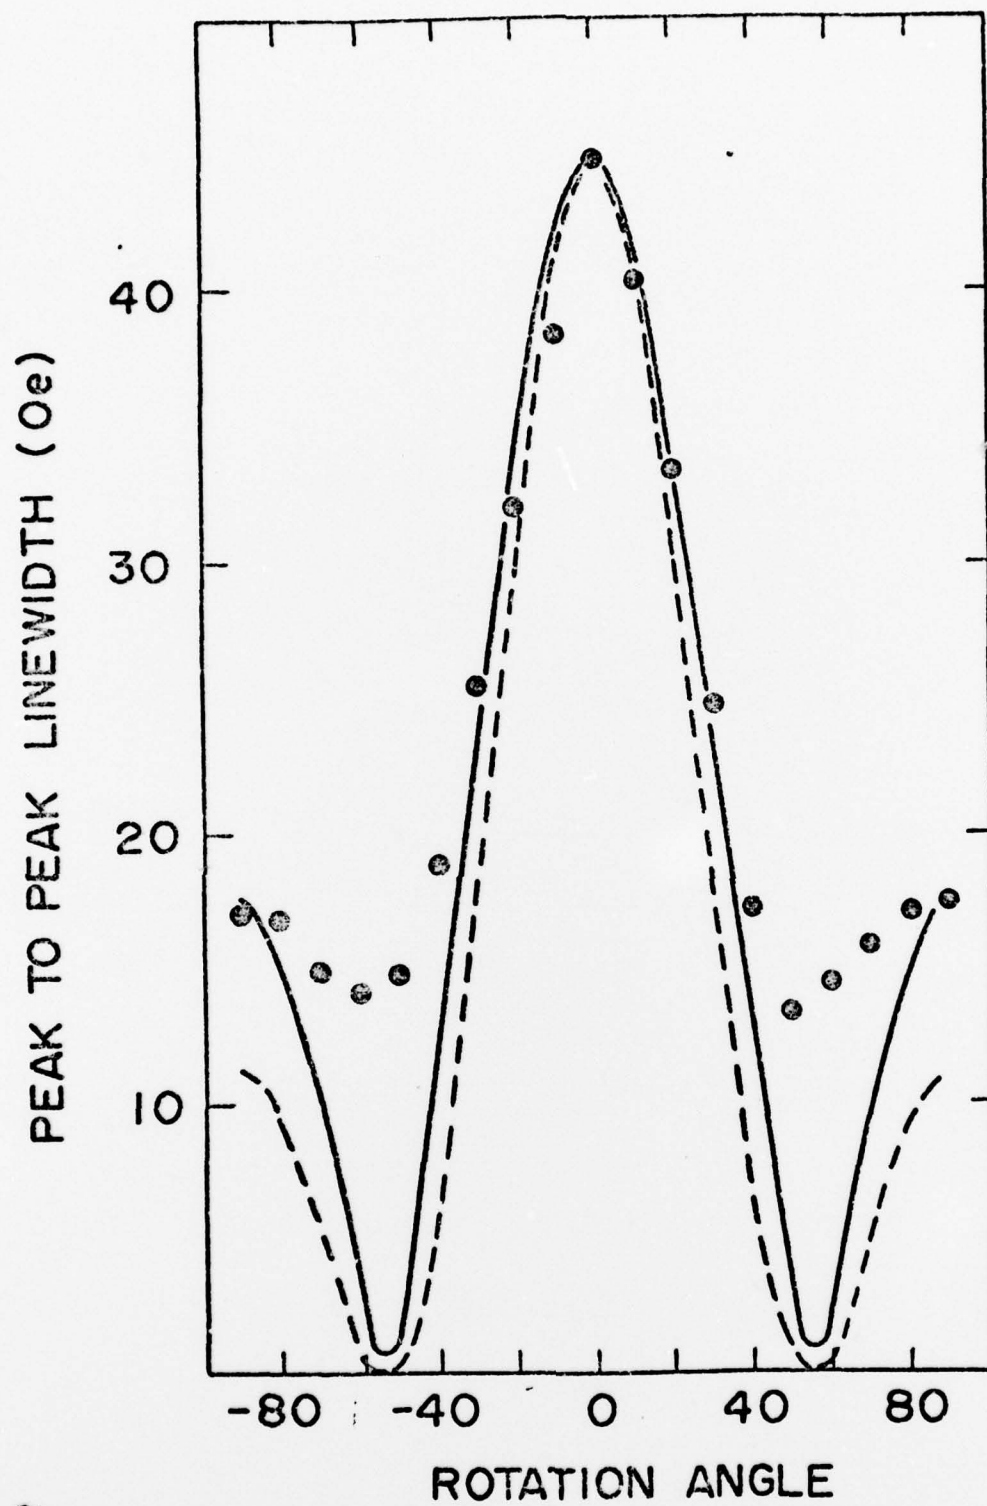

References

1. (a) Università di Siena, (b) University of Pennsylvania, (c) Pennwalt Corporation.
2. B. P. Block, Inorg. Macromol. Rev., 1, 115 (1970).
3. J. C. Scott, A. F. Garito, A. J. Heeger, P. Nannelli, and H. D. Gillman, Phys. Rev. B, 12, 356 (1975).
4. T. S. Wei, J. C. Scott, A. F. Garito, A. J. Heeger, H. D. Gillman, and P. Nannelli, Phys. Rev. B, 12, 5297 (1975).
5. W. C. Drinkard and G. M. Kosolapoff, J. Am. Chem. Soc., 74, 5520 (1952).
6. D. T. Cromer and J. T. Waber, Acta Crystallogr., 18, 104 (1965).
7. R. F. Stewart, E. R. Davidson, and W. T. Simpson, J. Chem. Phys., 42, 3175 (1965).
8. W. G. Waller and M. T. Rogers, J. Mag. Res., 9, 92 (1973).
9. J. C. Scott, A. F. Garito, and A. J. Heeger, Phys. Rev. B, 10, 3131 (1974).
10. P. Colamarino, P. L. Orioli, W. D. Benzinger, and H. D. Gillman, Inorg. Chem., 15, 800 (1976).
11. F. Giordano, L. Randaccio, and A. Ripamonti, Chem. Commun., 19, 1239 (1967); Acta Crystallogr., Sect. B, 25, 1057 (1969).
12. V. Giancotti and A. Ripamonti, J. Chem. Soc. A, 706 (1969).
13. V. Giancotti, F. Giordano, and A. Ripamonti, Makromol. Chem., 120, 96 (1968).

TABLE 1

POSITIONAL PARAMETERS (X 10⁴), THERMAL PARAMETERS (ANGSTRÖM² X 10³) AND ESTIMATED STANDARD DEVIATIONS FOR THE ATOMS OF BIS(DIBUTYLPHOSPHINATO)COPPER(II).

ATOM	X/A	Y/B	Z/C	U11	U22	U33	U12	J13	J23
CJ	113(1)	257(1)	2588(1)	46(0)	51(0)	24(0)	15(0)	19(0)	12(0)
P(1)	1389(1)	-938(2)	5235(2)	51(1)	51(1)	27(1)	21(1)	20(1)	13(1)
P(2)	1598(1)	-480(2)	381(2)	43(1)	65(1)	27(1)	15(1)	18(1)	16(1)
S(1)	1097(3)	-858(4)	3647(4)	66(3)	78(3)	28(2)	41(2)	28(2)	20(2)
S(2)	378(3)	-1164(4)	5799(4)	54(3)	56(3)	29(2)	18(2)	25(2)	9(2)
S(3)	1058(3)	452(4)	1350(4)	54(3)	62(3)	32(2)	12(2)	28(2)	17(2)
S(4)	1307(3)	-319(4)	-1184(4)	49(3)	94(3)	32(2)	19(2)	21(2)	24(2)
ATOM	X/A	Y/B	Z/C	J	AT9M	X/A	Y/B	Z/C	U
C(1)	2180(5)	-2399(6)	5388(6)	51(2)	C(9)	3133(6)	-42(7)	1097(7)	60(2)
C(2)	1522(6)	-3740(7)	4512(7)	70(2)	C(10)	3490(7)	1458(8)	1104(8)	79(2)
C(3)	2221(7)	-4985(9)	4540(9)	96(3)	C(11)	4771(8)	1901(10)	1636(10)	115(3)
C(4)	1555(9)	-6289(11)	3660(11)	133(4)	C(12)	5094(9)	3395(11)	1639(11)	133(4)
C(5)	2318(5)	582(6)	6328(6)	52(2)	C(13)	1255(5)	-2268(7)	400(7)	59(2)
C(6)	3373(6)	962(7)	5870(7)	64(2)	C(14)	1749(6)	-3316(8)	-561(8)	81(2)
C(7)	4113(7)	2236(8)	6797(9)	90(3)	C(15)	1417(8)	-4788(10)	-503(10)	114(3)
C(8)	5170(8)	2611(10)	6323(10)	120(3)	C(16)	1855(9)	-5867(11)	-1442(12)	146(4)

(CONTINUED OVER)

(CONTINUED TABLE 1)

ATOM	X/A	Y/B	Z/C	U	AT9M	X/A	Y/B	Z/C	U
H(1)	2521	-2361	5448	51	H(19)	3305	-172	2150	60
H(2)	2899	-2195	5119	51	H(20)	3468	-676	532	60
H(3)	974	-3825	3573	70	H(21)	3303	1586	0	79
H(4)	826	-4027	4835	70	H(22)	3323	2555	1710	79
H(5)	2884	-4586	4153	96	H(23)	4847	1507	2513	115
H(6)	2513	-5077	5733	96	H(24)	5151	1316	1005	115
H(7)	717	-6367	3173	133	H(25)	4656	3861	2355	133
H(8)	1945	-6617	2911	133	H(26)	4969	3592	743	133
H(9)	1693	-6995	4266	133	H(27)	6180	3703	2082	133
H(10)	1834	1223	6203	52	H(28)	528	-2310	0	59
H(11)	2621	548	7358	52	H(29)	1583	-2366	1400	59
H(12)	3723	0	5761	64	H(30)	1424	-3124	-1522	81
H(13)	3223	712	4800	64	H(31)	2503	-3216	-135	81
H(14)	3861	3061	7370	90	H(32)	587	-4936	-739	114
H(15)	4508	1826	7519	90	H(33)	1716	-4926	476	114
H(16)	4774	2931	5587	120	H(34)	2627	-5573	-1086	146
H(17)	5601	1753	6343	120	H(35)	1280	-5816	-2553	146
H(18)	5656	3395	7077	120	H(36)	1636	-6812	-1343	146

* ANISOTROPIC THERMAL FACTORS ARE OF THE FORM :

$$\exp(-2\pi^2 \sum_{i=1}^3 \sum_{j=1}^3 h_i h_j a_i^* a_j^* U_{ij})$$

TABLE 2

Bond lengths (Å) and angles (°) with estimated standard deviations in parentheses .

Cu-O(1)	1.919(4)	O(1)-Cu-O(2) ^{II}	95.7(2)
Cu-O(2) ^{II}	1.926(4)	O(1)-Cu-O(3)	93.7(2)
Cu-O(3)	1.919(4)	O(1)-Cu-O(4) ^I	147.2(2)
Cu-O(4) ^I	1.916(4)	O(2) ^{II} -Cu-O(3)	145.8(2)
		O(2) ^{II} -Cu-O(4) ^I	93.7(2)
		O(3)-Cu-O(4) ^I	96.0(2)
		Cu-O(1)-P(1)	130.8(3)
		Cu-O(2) ^{II} -P(1) ^{II}	135.8(2)
		Cu-O(3)-P(2)	137.9(3)
		Cu-O(4) ^I -P(2) ^I	132.4(3)
P(1)-O(1)	1.521(4)	O(1)-P(1)-O(2)	115.4(2)
P(1)-O(2)	1.508(5)	O(1)-P(1)-O(3)	105.8(3)
P(1)-O(3)	1.780(7)	O(1)-P(1)-O(5)	109.6(3)
P(1)-O(5)	1.783(5)	O(2)-P(1)-O(3)	107.9(3)
		O(2)-P(1)-O(5)	110.3(3)
		O(3)-P(1)-O(5)	107.5(3)
P(2)-O(3)	1.507(4)	O(3)-P(2)-O(4)	115.7(2)
P(2)-O(4)	1.522(4)	O(3)-P(2)-O(9)	107.8(2)
P(2)-O(9)	1.809(6)	O(3)-P(2)-O(13)	110.5(3)
P(2)-O(13)	1.790(7)	O(4)-P(2)-O(9)	105.4(3)
		O(4)-P(2)-O(13)	109.2(3)
		O(9)-P(2)-O(13)	108.0(3)

(Continued over)

(continued table 2)

C(1)-C(2)	1.48(1)	P(1)-C(1)-C(2)	113.6(4)
C(2)-C(3)	1.54(1)	C(1)-C(2)-C(3)	114.1(5)
C(3)-C(4)	1.45(1)	C(2)-C(3)-C(4)	112.9(7)
C(5)-C(6)	1.53(1)	P(1)-C(5)-C(6)	116.3(4)
C(6)-C(7)	1.48(1)	C(5)-C(6)-C(7)	114.5(6)
C(7)-C(8)	1.54(1)	C(6)-C(7)-C(8)	114.1(7)
C(9)-C(10)	1.51(1)	P(2)-C(9)-C(10)	111.0(5)
C(10)-C(11)	1.52(1)	C(9)-C(10)-C(11)	114.6(7)
C(11)-C(12)	1.50(2)	C(10)-C(11)-C(12)	113.1(8)
C(13)-C(14)	1.53(1)	P(2)-C(13)-C(14)	115.1(6)
C(14)-C(15)	1.50(1)	C(13)-C(14)-C(15)	112.1(7)
C(15)-C(16)	1.50(2)	C(14)-C(15)-C(16)	114.8(9)

.....

TECHNICAL REPORT DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. T. C. Williams Union Carbide Corp. Chemicals & Plastics Tarrytown Technical Center Tarrytown, New York 10591	1	Dr. M. Good Department of Chemistry University of New Orleans Lakefront New Orleans, Louisiana 70122	1
Dr. K. A. Reynard Horizons Inc. 23800 Mercantile Road Cleveland, Ohio 44122	1	Douglas Aircraft Co. 3855 Lakewood Boulevard Long Beach, California 90846 Attn: Technical Library CI 290/36-84 AUTO-Sutton	1
Dr. A. G. MacDiarmid University of Pennsylvania Department of Chemistry Philadelphia, Pennsylvania 19174	1	NASA-Lewis Research Center 21000 Brookpark Road Cleveland, Ohio 44135 Attn: Dr. T. T. Serafini, MS 49-1	1
Dr. E. Hedaya Union Carbide Corp. Corporate Research Laboratory Tarrytown Technical Center Tarrytown, New York 10591	1	Dr. J. Griffith Naval Research Laboratory Chemistry Section, Code 6120 Washington, D. C. 20375	1
Dr. A. Rheingold SUNY Plattsburg Department of Chemistry Plattsburg, New York 12901	1	Dr. G. Goodman Globe-Union Inc. 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. C. Pittman University of Alabama Department of Chemistry University, Alabama 35486	1	Dr. E. Fischer, Code 2853 Naval Ship Research and Development Center Annapolis Division Annapolis, Maryland 21402	1
Dr. H. Allcock Pennsylvania State University University Park, Pennsylvania 16802	1	Dr. Martin H. Kaufman, Head Materials Research Branch (Code 4542) Naval Weapons Center China Lake, California 93555	1
Dr. M. Kenney Case-Western University Department of Chemistry Cleveland, Ohio 44106	1	Professor Lydia M. Frenzel University of New Orleans Department of Chemistry New Orleans, Louisiana 70122	1
Dr. R. Lenz Department of Chemistry University of Massachusetts Amherst, Massachusetts 01002	1		

TECHNICAL REPORT DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Arlington, Virginia 22217 Attn: Code 472	2	Defense Documentation Center Building 5, Cameron Station Alexandria, Virginia 22314	12
Office of Naval Research Arlington, Virginia 22217 Attn: Code 102IP	6	U. S. Army Research Office P. O. Box 12211 Research Triangle Park, N. C. 27709 Attn: CRD-AA-IP	1
ONR Branch Office 536 S. Clark Street Chicago, Illinois 60605 Attn: Dr. George Sandoz	1	Commander Naval Undersea Research & Development Center San Diego, California 92132 Attn: Technical Library, Code 133	1
ONR Branch Office 715 Broadway New York, New York 10003 Attn: Scientific Dept.	1	Naval Weapons Center China Lake, California 93555 Attn: Head, Chemistry Division	1
ONR Branch Office 1030 East Green Street Pasadena, California 91106 Attn: Dr. R. J. Marcus	1	Naval Civil Engineering Laboratory Port Hueneme, California 93041 Attn: Mr. W. S. Haynes	1
ONR Branch Office 760 Market Street, Rm. 447 San Francisco, California 94102 Attn: Dr. P. A. Miller	1	Professor O. Heinz Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
ONR Branch Office 495 Summer Street Boston, Massachusetts 02210 Attn: Dr. L. H. Peebles	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D. C. 20380	1
Director, Naval Research Laboratory Washington, D. C. 20390 Attn: Library, Code 2029 (ONRL)	6		
Technical Info. Div.	1		
Code 6100, 6170	1		
The Asst. Secretary of the Navy (R&D) Department of the Navy Room 4E736, Pentagon Washington, D. C. 20350	1		
Commander, Naval Air Systems Command Department of the Navy Washington, D. C. 20360 Attn: Code 310C (H. Rosenwasser)	1		