

AD-A074 236

OKLAHOMA UNIV NORMAN SCHOOL OF AEROSPACE MECHANICAL --ETC F/6 12/1
A PENALTY PLATE-BENDING ELEMENT FOR THE ANALYSIS OF LAMINATED A--ETC(U)
AUG 79 J N REDDY

N00014-78-C-0647

UNCLASSIFIED


OU-AMNE-79-14

NL

| OF |
AD
A074236



END
DATE
FILMED
10-79
DDC

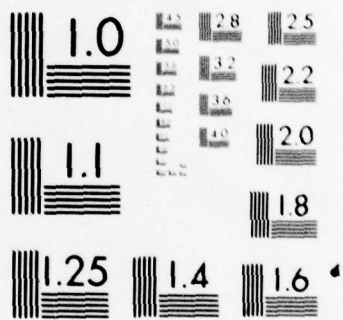

MICROCOPY RESOLUTION TEST CHART
 NATIONAL BUREAU OF STANDARDS-1963-A

LEVEL II

12

Department of the Navy
OFFICE OF NAVAL RESEARCH
Structural Mechanics Program
Arlington, Virginia 22217

Contract N00014-78-C-0647
Project NR 064-609
Technical Report No. 6

DDC
RECEIVED
SEP 19 1979
C

AD A 074236

Report OU-AMNE-79-14

A PENALTY PLATE-BENDING ELEMENT FOR THE ANALYSIS
OF LAMINATED ANISOTROPIC COMPOSITE PLATES

See 1473 in books

by

J. N. Reddy

August 1979

DDC FILE COPY

School of Aerospace, Mechanical and Nuclear Engineering
University of Oklahoma
Norman, Oklahoma 73019

400 498

Approved for public release; distribution unlimited

79 09 18 132

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER 14 OU-AMNE-79-14 TR-6	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE AND SUBTITLE 6 A PENALTY PLATE-BENDING ELEMENT FOR THE ANALYSIS OF LAMINATED ANISOTROPIC COMPOSITE PLATES		5. TYPE OF REPORT & PERIOD COVERED Technical Report
6. AUTHOR(s) 10 J. N./Reddy		7. PERFORMING ORG. REPORT NUMBER
8. CONTRACT OR GRANT NUMBER(s)		15 N00014-78-C-0647
9. PERFORMING ORGANIZATION NAME AND ADDRESS School of Aerospace, Mechanical and Nuclear Engineering University of Oklahoma, Norman, OK 73019		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 064-609
11. CONTROLLING OFFICE NAME AND ADDRESS Department of the Navy, Office of Naval Research Structural Mechanics Program (Code 474) Arlington, Virginia 22217		12. REPORT DATE 11 Aug 79
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		13. NUMBER OF PAGES 34
12 37 p.		13. SECURITY CLASS. (of this report) UNCLASSIFIED
16. DISTRIBUTION STATEMENT (of this Report) This document has been approved for public release and sale; distribution unlimited.		13a. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Results contained in the report are to be presented at the Sixteenth Annual Meeting of the Society of Engineering Science, Northwestern University, Evanston, ILL, Sept. 5-7, 1979		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Bending stresses, bending deflections, fiber-reinforced composites, finite elements, laminated plates, mixed finite element method, natural frequencies, penalty method, shear flexible plate theory, variational formulations		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) A C^0 (penalty) finite element is developed for the equations governing the heterogeneous laminated plate theory of Yang, Norris and Stavsky. The YNS theory is a generalization of Mindlin's theory for homogeneous, isotropic plates to arbitrarily laminated anisotropic plates and includes shear deformation and rotary inertia effects. The present element can also be used in the analysis of thin plates by appropriately specifying the penalty parameter. A variety of problems are solved, including those for which (over) <i>degrees</i>		

DD FORM 1473 JAN 73

EDITION OF 1 NOV 68 IS OBSOLETE S/N 0102-014-6601

UNCLASSIFIED SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

400 498

slh

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

20. Abstract - Cont'd

solutions are not available in the literature, to show the material effects and the parametric effects of plate aspect ratio, length-to-thickness ratio, lamination scheme, number of layers and lamination angle on the deflections, stresses, and vibration frequencies. Despite its simplicity, the present element gives very accurate results.



SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

A PENALTY PLATE-BENDING ELEMENT FOR THE ANALYSIS
OF LAMINATED ANISOTROPIC COMPOSITE PLATES

J. N. Reddy

School of Aerospace, Mechanical and Nuclear Engineering
The University of Oklahoma, Norman, OK 73019

Accession For	
NTIS GMA&I	<input checked="" type="checkbox"/>
DDC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/	
Availability Codes	
Dist	Avail and/or special
A	

SUMMARY

A C^0 (penalty) finite element is developed for the equations governing the heterogeneous laminated plate theory of Yang, Norris and Stavsky. The YNS theory is a generalization of Mindlin's theory for homogeneous, isotropic plates to arbitrarily laminated anisotropic plates and includes shear deformation and rotary inertia effects. The present element can also be used in the analysis of thin plates by appropriately specifying the penalty parameter. A variety of problems are solved, including those for which solutions are not available in the literature, to show the material effects and the parametric effects of plate aspect ratio, length-to-thickness ratio, lamination scheme, number of layers and lamination angle on the deflections, stresses, and vibration frequencies. Despite its simplicity, the present element gives very accurate results.

INTRODUCTION

Over the past few years composites, especially fiber-reinforced laminates, have found increasing application in many engineering structures. The fiber-reinforced composites possess two desirable features: one is their high stiffness-to-weight ratio, and the other is their anisotropic material property that can be tailored through variation of the fiber orientation

and stacking sequence--a feature which gives the designer an added degree of flexibility.

Recent developments in the analysis of plates laminated of fiber-reinforced materials indicate that the thickness effect on the behavior of the plate is more pronounced than in isotropic plates. The classical thin plate theory assumes that normals to the midsurface before deformation remain straight and normal to the midsurface after deformation, implying that transverse shear deformation effects are negligible. As a result, the free vibration frequencies, for example, calculated using the thin plate theory are higher than those obtained by the Mindlin plate theory¹, which includes transverse shear and rotary inertia effects; the deviation increases with increasing mode number. Higher order linear theories that include transverse shear effects have also appeared (see Reissner² and Lo, Christensen, and Wu³). Elasticity solutions by Pagano and his associates⁴⁻⁷ indicate the inadequacy of the classical laminated plate theory (e.g., Reissner and Stavsky⁸, Dong et al.⁹, and Bert and Mayberry¹⁰, in which the classical Kirchhoff-Love kinematic assumptions are adopted and effects of transverse shear deformations are neglected. The transverse shear deformation effects are even more pronounced, due to the low transverse shear modulus relative to the in-plane Young's moduli, in the case of filamentary composite plates. A reliable prediction of the response characteristics of high modulus composite plates requires the use of shear deformable theories.

A number of shear deformable theories for laminates have been proposed to date. The first such theory for laminated isotropic plates is due to Stavsky¹¹. The theory has been generalized to laminated anisotropic plates

by Yang, Norris, and Stavsky¹². A review of various other theories, for example, the effective stiffness theory of Sun and Whitney¹², the higher-order theory of Whitney and Sun¹⁴, and the three-dimensional elasticity theory of Srinivas and Rao¹⁵, can be found in the paper by Bert¹⁶. Other approximate theories that have been proposed in the literature include the refined laminated plate theory of Mau¹⁷, the continuum theory of Sun, Achenbach, and Herrmann¹⁸, and diffusing continuum theory of Bedford and Stern¹⁹ which were primarily developed for use in wave-propagation problems. It has been shown, see for example, the papers by Sun and Whitney¹³ and Srinivas and Rao¹⁵, that the Yang-Norris-Stavsky (YNS) theory is adequate for predicting the overall behavior such as transverse deflections and natural frequencies (first few modes) of laminated anisotropic plates.

The first application of the YNS theory is apparently due to Whitney and Pagano²⁰, who considered cylindrical bending of antisymmetric cross-ply and angle-ply plate strips under sinusoidal load distribution and free vibration of antisymmetric angle-ply plate strips. Fortier and Rosettos²¹ analyzed free vibration of thick rectangular plates of unsymmetric cross-ply construction while Sinha and Rath²² considered both vibration and buckling for the same type of plates. Recently, Bert and Chen²³ presented, using the YNS theory, a closed-form solution for the free vibration of simply supported rectangular plates of antisymmetric angle-ply laminates.

While considerable effort has been expended in the finite-element analysis of isotropic plates, only limited investigations of laminated anisotropic plates can be found in the literature. Pryor and Barker²⁴, and Barker, Lin and Dara²⁵ used the conventional displacement finite-element

method to analyze thick laminated plates. The element has seven degrees of freedom (three displacements, two rotations, and two shear rotations) per node. Exploiting the symmetries exhibited by anisotropic plates, Noor and Mathers²⁶⁻²⁸ studied the effects of shear deformation and anisotropy on the accuracy and convergence of several shear-flexible displacement finite element models based on a form of Reissner's plate theory. The analysis was limited to symmetrically laminated cross-ply plates and the element used involved 80 degrees of freedom per element. The conventional finite element, when applied to relatively thick laminated plates, either has failed to predict accurately the local deformations and stresses of a plate under bending or is too expensive to use due to the large number of degrees of freedom involved for even relatively simple problems. Mau and Witmer²⁹ and Mau, Tong, Pian³⁰ have employed the so-called hybrid-stress finite-element method to analyze composite plates including shear deformation. The hybrid elements have proven (see Gallagher³¹) to have some convergence problems, and in some cases they give erroneous results. Most recently, Panda and Natarajan³² used, following Mawanya and Davies³³, the quadratic shell element of Ahmad, Irons and Zienkiewicz³⁴ with the same normal rotation through the thickness to claim improved accuracy over Mawanya and Davies³³. The 'thickness concept' mentioned there is essentially the same as that used in the YNS theory¹². The authors were primarily concerned with the accuracy of the element, and no attempt was made to solve new problems for which there do not exist any closed-form or exact solutions.

The present paper is concerned with the development of a simple C^0 element for YNS theory of laminated composite plates. The penalty function

concept of Courant³⁵ (also see Zienkiewicz³⁶) is used to develop the finite element model. The element contains five degrees of freedom, three displacements and two slopes (i.e. shear rotations), per node. The accuracy of the element is demonstrated via problems for which the exact solutions and numerical results are available, and results are also presented for a variety of problems for which solutions are not available in the literature.

LAMINATED PLATE THEORY OF YANG-NORRIS-STAVSKY (YNS)

Consider a plate of constant thickness h composed of a finite number, L , of thin anisotropic layers oriented at angles $\theta_1, \theta_2, \dots, \theta_L$. The origin of the coordinate system is located within the middle plane (x - y) with the z -axis being normal to the mid-plane. The material of each layer is assumed to possess a plane of elastic symmetry parallel to the xy -plane. We shall denote the middle plane with Ω .

The YNS theory is based on the following assumed displacement field:

$$\begin{aligned} u &= u_0(x,y,t) + z\psi_x(x,y,t) \\ v &= v_0(x,y,t) + z\psi_y(x,y,t) \\ w &= w(x,y,t) \end{aligned} \tag{1}$$

where u , v , and w are the displacement components in the x , y , and z directions, respectively, t is the time, u_0 and v_0 are the in-plane (stretching) displacements of the middle plane, and ψ_x and ψ_y are the shear rotations. Recalling the strain-displacement equations of linear elasticity, we have

$$\begin{aligned}\epsilon_x &= \frac{\partial u_0}{\partial x} + z \frac{\partial \psi_x}{\partial x}, \quad \epsilon_y = \frac{\partial v_0}{\partial y} + z \frac{\partial \psi_y}{\partial y}, \quad \epsilon_z = 0 \\ \gamma_{xy} &= \frac{\partial u_0}{\partial y} + \frac{\partial v_0}{\partial x} + z \left(\frac{\partial \psi_x}{\partial y} + \frac{\partial \psi_y}{\partial x} \right), \\ \gamma_{xz} &= \psi_x + \frac{\partial w}{\partial x}, \quad \gamma_{yz} = \psi_y + \frac{\partial w}{\partial y}\end{aligned}\tag{2}$$

Owing to the existence of a plane of elastic symmetry, the constitutive relations for any layer in the (x,y) system are given by

$$\begin{bmatrix} \sigma_x \\ \sigma_y \\ \tau_{yz} \\ \tau_{xz} \\ \tau_{xy} \end{bmatrix} = \begin{bmatrix} Q_{11} & Q_{12} & 0 & 0 & Q_{16} \\ Q_{12} & Q_{22} & 0 & 0 & Q_{26} \\ 0 & 0 & Q_{44} & Q_{45} & 0 \\ 0 & 0 & Q_{45} & Q_{55} & 0 \\ Q_{16} & Q_{26} & 0 & 0 & Q_{66} \end{bmatrix} \begin{bmatrix} \epsilon_x \\ \epsilon_y \\ \gamma_{yz} \\ \gamma_{xz} \\ \gamma_{xy} \end{bmatrix}\tag{3}$$

where Q_{ij} are the (material) stiffness components.

Introducing the stress and moment resultants per unit length,

$$(N_1, N_2, N_6) = \int_{-h/2}^{h/2} (\sigma_x, \sigma_y, \tau_{xy}) dz, \quad (Q_x, Q_y) = \int_{-h/2}^{h/2} (\tau_{xz}, \tau_{yz}) dz\tag{4}$$

$$(M_1, M_2, M_6) = \int_{-h/2}^{h/2} (\sigma_x, \sigma_y, \tau_{xy}) z dz$$

we can write (2) and (3) in terms of the resultants and displacements:

$$\begin{bmatrix} N_1 \\ N_2 \\ Q_y \\ Q_x \\ N_6 \\ M_1 \\ M_2 \\ M_6 \end{bmatrix} = \begin{bmatrix} A_{11} & A_{12} & 0 & 0 & A_{16} & B_{11} & B_{12} & B_{16} \\ A_{12} & A_{22} & 0 & 0 & A_{16} & B_{12} & B_{22} & B_{26} \\ 0 & 0 & A_{44} & A_{45} & 0 & 0 & 0 & 0 \\ 0 & 0 & A_{45} & A_{55} & 0 & 0 & 0 & 0 \\ A_{16} & A_{26} & 0 & 0 & A_{66} & B_{16} & B_{26} & B_{66} \\ B_{11} & B_{12} & 0 & 0 & B_{16} & D_{11} & D_{12} & D_{16} \\ B_{12} & B_{22} & 0 & 0 & B_{26} & D_{12} & D_{22} & D_{26} \\ B_{16} & B_{26} & 0 & 0 & B_{66} & D_{16} & D_{26} & D_{66} \end{bmatrix} \begin{bmatrix} u_{0,x} \\ v_{0,y} \\ w_{,y} + \psi_y \\ w_{,x} + \psi_x \\ u_{0,y} + v_{0,x} \\ \psi_{x,x} \\ \psi_{y,y} \\ \psi_{x,y} + \psi_{y,x} \end{bmatrix} \quad (5)$$

The material components A_{ij} , B_{ij} , and D_{ij} are given by

$$(A_{ij}, B_{ij}, D_{ij}) = \int_{-h/2}^{h/2} Q_{ij}^{(m)} (1, z, z^2) dz, \quad (i, j = 1, 2, 6) \quad (6)$$

$$A_{ij} \equiv k_\alpha k_\beta \bar{A}_{ij}, \quad \bar{A}_{ij} = \int_{-h/2}^{h/2} Q_{ij}^{(m)} dz, \quad (i, j = 4, 5), \quad \alpha = 6-i, \quad \beta = 6-j$$

The stiffness coefficients $Q_{ij}^{(m)}$ depend on the material properties and orientation of the m -th layer. The parameters k_i are the shear correction coefficients.

The equations of motion associated with YNS theory are

$$\frac{\partial N_1}{\partial x} + \frac{\partial N_6}{\partial y} = p \frac{\partial^2 u}{\partial t^2} + R \frac{\partial^2 \psi_x}{\partial t^2}$$

$$\frac{\partial N_6}{\partial x} + \frac{\partial N_2}{\partial y} = p \frac{\partial^2 v}{\partial t^2} + R \frac{\partial^2 \psi_y}{\partial t^2}$$

$$\frac{\partial Q_x}{\partial x} + \frac{\partial Q_y}{\partial y} = p \frac{\partial^2 w}{\partial t^2} - P$$

$$\frac{\partial M_1}{\partial x} + \frac{\partial M_6}{\partial y} - Q_x = I \frac{\partial^2 \psi_x}{\partial t^2} + R \frac{\partial^2 u}{\partial t^2} \quad (7)$$

$$\frac{\partial M_6}{\partial x} + \frac{\partial M_2}{\partial y} - Q_y = I \frac{\partial^2 \psi_y}{\partial t^2} + R \frac{\partial^2 v}{\partial t^2}$$

where

$$(p, R, I) = \int_{-h/2}^{h/2} (1, z, z^2) \rho^{(m)} dz \quad (8)$$

$\rho^{(m)}$ being the material density of layer m , and $P = P(x, y)$ is the transversely distributed load.

The strain energy and the kinetic energy, for a fixed time t , are given by

$$U = U_1 + U_2 \quad (9)$$

$$T = \frac{1}{2} \int_{\Omega} \left\{ p \left[\left(\frac{\partial u}{\partial t} \right)^2 + \left(\frac{\partial v}{\partial t} \right)^2 + \left(\frac{\partial w}{\partial t} \right)^2 \right] + I \left[\left(\frac{\partial \psi_x}{\partial t} \right)^2 + \left(\frac{\partial \psi_y}{\partial t} \right)^2 \right] + 2R \left[\frac{\partial \psi_x}{\partial t} \frac{\partial u}{\partial t} + \frac{\partial \psi_y}{\partial t} \frac{\partial v}{\partial t} \right] \right\} dx dy \quad (10)$$

where

$$\begin{aligned} U_1 = \frac{1}{2} \int_{\Omega} & \left(A_{11} \left(\frac{\partial u_0}{\partial x} \right)^2 + 2A_{16} \frac{\partial u_0}{\partial x} \frac{\partial u_0}{\partial y} + A_{66} \left(\frac{\partial u_0}{\partial y} \right)^2 + \left(A_{12} \frac{\partial v_0}{\partial y} + A_{16} \frac{\partial v_0}{\partial x} \right) \frac{\partial v_0}{\partial y} \right. \\ & + \frac{\partial v_0}{\partial y} \left(A_{12} \frac{\partial u_0}{\partial x} + A_{26} \frac{\partial u_0}{\partial y} \right) + \frac{\partial u_0}{\partial y} \left(A_{26} \frac{\partial v_0}{\partial y} + A_{66} \frac{\partial v_0}{\partial x} \right) \\ & + \frac{\partial v_0}{\partial x} \left(A_{16} \frac{\partial u_0}{\partial x} + A_{66} \frac{\partial u_0}{\partial y} \right) + A_{22} \left(\frac{\partial v_0}{\partial y} \right)^2 + 2A_{16} \frac{\partial v_0}{\partial y} \frac{\partial v_0}{\partial x} \\ & + A_{66} \left(\frac{\partial v_0}{\partial x} \right)^2 + \frac{\partial u_0}{\partial x} \left(B_{11} \frac{\partial \psi_x}{\partial x} + B_{16} \frac{\partial \psi_x}{\partial y} + B_{12} \frac{\partial \psi_y}{\partial y} + B_{16} \frac{\partial \psi_y}{\partial x} \right) \\ & \left. + \left(\frac{\partial u_0}{\partial y} + \frac{\partial v_0}{\partial x} \right) \left(B_{16} \frac{\partial \psi_x}{\partial x} + B_{66} \frac{\partial \psi_x}{\partial y} + B_{26} \frac{\partial \psi_y}{\partial y} + B_{66} \frac{\partial \psi_y}{\partial x} \right) \right) \end{aligned}$$

$$\begin{aligned}
& + \frac{\partial v_0}{\partial y} (B_{12} \frac{\partial \psi_x}{\partial x} + B_{26} \frac{\partial \psi_x}{\partial y} + B_{22} \frac{\partial \psi_y}{\partial y} + B_{26} \frac{\partial \psi_y}{\partial x}) + \frac{\partial \psi_x}{\partial x} (B_{11} \frac{\partial u_0}{\partial x} \\
& + B_{16} \frac{\partial u_0}{\partial y} + B_{12} \frac{\partial v_0}{\partial y} + B_{16} \frac{\partial v_0}{\partial x}) + (\frac{\partial \psi_x}{\partial y} + \frac{\partial \psi_y}{\partial x}) (B_{16} \frac{\partial u_0}{\partial x} + B_{66} \frac{\partial u_0}{\partial y} \\
& + B_{26} \frac{\partial v_0}{\partial y} + B_{66} \frac{\partial v_0}{\partial x}) + \frac{\partial \psi_y}{\partial y} (B_{12} \frac{\partial u_0}{\partial x} + B_{26} \frac{\partial u_0}{\partial y} + B_{22} \frac{\partial v_0}{\partial y} + B_{26} \frac{\partial v_0}{\partial x}) \\
& + D_{11} (\frac{\partial \psi_x}{\partial x})^2 + 2D_{16} \frac{\partial \psi_x}{\partial x} \frac{\partial \psi_x}{\partial y} + D_{66} (\frac{\partial \psi_x}{\partial y})^2 + \frac{\partial \psi_x}{\partial x} (D_{12} \frac{\partial \psi_y}{\partial y} + 2D_{16} \frac{\partial \psi_y}{\partial x}) \\
& + \frac{\partial \psi_y}{\partial y} (D_{12} \frac{\partial \psi_x}{\partial x} + 2D_{26} \frac{\partial \psi_x}{\partial y}) + 2D_{66} \frac{\partial \psi_x}{\partial y} \frac{\partial \psi_y}{\partial x} + D_{22} (\frac{\partial \psi_y}{\partial y})^2 \\
& + 2D_{26} \frac{\partial \psi_y}{\partial x} \frac{\partial \psi_y}{\partial y} + D_{66} (\frac{\partial \psi_y}{\partial x})^2 \} dx dy \quad (11)
\end{aligned}$$

$$\begin{aligned}
U_2 = \frac{1}{2} \int_{\Omega} \{ [A_{44} (\frac{\partial w}{\partial x} + \psi_x) + A_{45} (\frac{\partial w}{\partial y} + \psi_y)] (\frac{\partial w}{\partial x} + \psi_x) + \\
[A_{45} (\frac{\partial w}{\partial x} + \psi_x) + A_{55} (\frac{\partial w}{\partial y} + \psi_y)] (\frac{\partial w}{\partial y} + \psi_y) \} dx dy \quad (12)
\end{aligned}$$

Note that the quantities in the square brackets of U_2 are the shear forces Q_x and Q_y , respectively.

PENALTY FUNCTION FORMULATION OF THE EQUATIONS

The assumption of the classical thin-plate theory that the normals to the midsurface before deformation remain straight and normal to the midsurface after deformation implies that

$$\psi_x = - \frac{\partial w}{\partial x} \quad , \quad \text{and} \quad \psi_y = - \frac{\partial w}{\partial y} \quad (13)$$

If we substitute for ψ_x and ψ_y from (13) into (11), we obtain the strain energy $U = U_1$ associated with the classical thin-plate theory. In that case U_1 involves the second-order derivatives of the transverse deflection, and the associated (conventional) finite-element formulation results in

complicated elements (with many degrees of freedom). Approaches that have been taken to relax the continuity requirements placed on the shape functions in the displacement formulation of the thin-plate theory include, in addition to the nonconforming, hybrid and mixed formulations, the "discrete Kirchhoff hypothesis" of Wempner, Oden and Kross³⁷, Fried³⁸, and the "residual energy balancing" and "reduced integration" techniques of Fried³⁹, Zienkiewicz, Taylor and Too⁴⁰, and Hughes, Taylor and Kanokukulchai⁴¹. The present penalty function method is a formalization and extension of these ideas to the shear deformable theory of laminated composite plates.

The problem of finding the static solution (u,v,w) to the thin plate equations can be viewed as one of finding the critical points of the total potential energy $\pi_1 = U_1 + V$, where U_1 is the strain energy given by (11) in terms of u , v and w , and V is the potential energy due to applied loads. Alternately, the problem can also be viewed as one of finding (u,v,ψ_x,ψ_y) subject to the constraint conditions in (13). To incorporate the constraints, one can use the Lagrange multiplier method, or the penalty function method.

If the Lagrange multiplier method is used, we have

$$U_L = U_1 + \int_{\Omega} [\lambda_x (\frac{\partial w}{\partial x} + \psi_x) + \lambda_y (\frac{\partial w}{\partial y} + \psi_y)] dx dy \quad (14)$$

where λ_x and λ_y are the Lagrange multipliers. Comparing the Euler equations of $\pi_L = U_L + V$ with those of $\pi = U + V$, we see that the Lagrange multipliers are given by,

$$\begin{aligned} \lambda_x &= Q_x \equiv A_{44} (\frac{\partial w}{\partial x} + \psi_x) + A_{45} (\frac{\partial w}{\partial y} + \psi_y) \\ \lambda_y &= Q_y \equiv A_{45} (\frac{\partial w}{\partial x} + \psi_x) + A_{55} (\frac{\partial w}{\partial y} + \psi_y) \end{aligned} \quad (15)$$

Thus, U_L is equivalent to the strain energy U of the shear deformable theory.

If the penalty function method is used, the modified functional is given by $\pi_p = U_1 + U_p + V$, wherein the penalty functional U_p is chosen to be

$$U_p = \frac{1}{2} \int_{\Omega} [\epsilon_1^2 \left(\frac{\partial w}{\partial x} + \psi_x\right)^2 + \epsilon_2^2 \left(\frac{\partial w}{\partial y} + \psi_y\right)^2 + 2\epsilon_1\epsilon_2 \left(\frac{\partial w}{\partial x} + \psi_x\right)\left(\frac{\partial w}{\partial y} + \psi_y\right)] dx dy \quad (16)$$

where ϵ_1^2 and ϵ_2^2 are the penalty parameters. Clearly, in the limits $\epsilon_1, \epsilon_2 \rightarrow \infty$, the constraints are satisfied exactly. As opposed to the Lagrange multiplier method the constraints are satisfied only approximately, and no additional variables are introduced in the penalty method. Comparing the Euler equations of the functional π_p with the equations of the YNS theory, we see the correspondence,

$$\begin{aligned} Q_x &\approx Q_x^e \equiv \epsilon_1^2 \left(\frac{\partial w}{\partial x} + \psi_x\right) + \epsilon_1\epsilon_2 \left(\frac{\partial w}{\partial y} + \psi_y\right) \\ Q_y &\approx Q_y^e \equiv \epsilon_2\epsilon_1 \left(\frac{\partial w}{\partial x} + \psi_x\right) + \epsilon_2^2 \left(\frac{\partial w}{\partial y} + \psi_y\right) \\ \epsilon_1^2 &\approx k_1^2 \bar{A}_{44}, \quad \epsilon_1\epsilon_2 \approx k_1 k_2 \bar{A}_{45}, \quad \epsilon_2^2 \approx k_2^2 \bar{A}_{55} \end{aligned} \quad (17)$$

This correspondence implies that for very large values of ϵ_i , the equations govern the thin-plate theory, and for values of ϵ_i given in (17), the equations coincide with the YNS theory.

FINITE-ELEMENT MODELS

Here we present a (semidiscrete) finite-element model based on $\pi_p(u, v, \psi_x, \psi_y, w)$. We assume, over each element Ω_e , the same kind of interpolation for all of the variables,

$$u_0^e = \sum_1^n u_1^e N_1^e, \quad v_0^e = \sum_1^n v_1^e N_1^e, \quad \text{etc.} \quad (n = \text{nodes per element}) \quad (18)$$

where N_i^e are the element interpolation (or shape) functions, and u_i^e , and v_i^e are the nodal values of u_0^e and v_0^e , respectively. Substituting (18) into the first variation of $\pi_p^e(u, v, w, \psi_x, \psi_y)$, and collecting the coefficients of the variations, δu_i , δv_i , etc., we obtain

$$[M^e]\{\ddot{\Delta}^e\} + [K^e]\{\Delta^e\} = \{F^e\} \quad (19)$$

where

$$\{\Delta^e\} = \begin{Bmatrix} \{u^e\} \\ \{v^e\} \\ \{w^e\} \\ \{\psi_x^e\} \\ \{\psi_y^e\} \end{Bmatrix}, \quad [M] = \begin{bmatrix} p[S^0] & & & & R[S^0] \\ & p[S^0] & & & R[S^0] \\ & & p[S^0] & & \\ & & & \text{symmetric} & I[S^0] \\ & & & & I[S^0] \end{bmatrix} \quad (20)$$

The elements $K_{ij}^{\alpha\beta}$ ($\alpha, \beta=1, 2, \dots, 5$; $i, j=1, 2, \dots, n$) of the stiffness matrix, S_{ij}^0 of the mass matrix are given by

$$K_{ij}^{11} = A_{11} S_{ij}^x + A_{16} (S_{ij}^{xy} + S_{ji}^{xy}) + A_{66} S_{ij}^y$$

$$K_{ij}^{12} = A_{12} S_{ij}^{xy} + A_{16} S_{ij}^x + A_{26} S_{ij}^y + A_{66} S_{ji}^{xy}$$

$$K_{ij}^{14} = B_{11} S_{ij}^x + B_{16} (S_{ij}^{xy} + S_{ji}^{xy}) + B_{66} S_{ij}^y$$

$$K_{ij}^{15} = B_{12} S_{ij}^{xy} + B_{16} S_{ij}^x + B_{26} S_{ij}^y + B_{66} S_{ji}^{xy}$$

$$K_{ij}^{22} = A_{26} (S_{ij}^{xy} + S_{ji}^{xy}) + A_{22} S_{ij}^y + A_{66} S_{ij}^x$$

$$K_{ij}^{24} = B_{16} S_{ij}^x + B_{66} S_{ij}^{xy} + B_{12} S_{ji}^{xy} + B_{26} S_{ij}^y$$

$$K_{ij}^{25} = B_{26} (S_{ij}^{xy} + S_{ji}^{xy}) + B_{66} S_{ij}^x + B_{22} S_{ij}^y$$

$$\begin{aligned}
K_{ij}^{33} &= \epsilon_1^2 S_{ij}^x + \epsilon_2^2 S_{ij}^y + \epsilon_1 \epsilon_2 (S_{ij}^{xy} + S_{ij}^{yx}) \\
K_{ij}^{34} &= \epsilon_1^2 S_{ij}^{x0} + \epsilon_1 \epsilon_2 S_{ij}^{y0} , \quad K_{ij}^{35} = \epsilon_1 \epsilon_2 S_{ij}^{x0} + \epsilon_2^2 S_{ij}^{y0} \\
K_{ij}^{44} &= D_{11} S_{ij}^x + D_{16} (S_{ij}^{xy} + S_{ji}^{yx}) + D_{66} S_{ij}^y + \epsilon_1^2 S_{ij}^0 \\
K_{ij}^{45} &= D_{12} S_{ij}^{xy} + D_{66} S_{ji}^{yx} + D_{16} S_{ij}^x + D_{26} S_{ij}^y + \epsilon_1 \epsilon_2 S_{ij}^0 \\
K_{ij}^{55} &= D_{26} (S_{ij}^{xy} + S_{ji}^{yx}) + D_{66} S_{ij}^x + D_{22} S_{ij}^y + \epsilon_2^2 S_{ij}^0 \\
K_{ij}^{13} &= K_{ij}^{23} = 0 , \quad S_{ij}^{\xi\eta} = \int_{\Omega^e} N_{i,\xi} N_{j,\eta} dx dy , \quad (\xi, \eta = 0, x, y) \\
F_i^3 &= \int_{\Omega^e} P N_i dx dy , \quad F_i^1 = F_i^2 = F_i^4 = F_i^5 = 0 \quad (21)
\end{aligned}$$

For free vibration, equation (19) becomes

$$([K^e] - \omega^2 [M^e]) \{\Delta^e\} = \{0\} \quad (22)$$

where ω is the frequency of the natural vibration. For static analysis, $\{\ddot{\Delta}\}$ is set to zero. The element stiffness matrices are assembled in the usual manner, and boundary conditions of the problem are imposed before solving for $\{\Delta\}$ or ω_n .

In the present study linear ($n=4$) and quadratic ($n=8$) elements of the serendepity family are used. The element stiffness matrices for these elements are of order 20×20 , and 40×40 , respectively.

NUMERICAL EXAMPLES AND DISCUSSION

The (penalty) finite element developed herein was employed in the bending and free vibration analyses of a variety of layered composite rectangular plates. All of the numerical results presented here were obtained using a uniform mesh of 2x2 quadratic (i.e. 8-node quadrilateral) elements in the quarter plate. Computations were conducted on an IBM 370/158 computer in single precision.

In the following analyses two types of boundary conditions, simply supported and clamped, and two types of orthotropic materials were used. The coordinate system and boundary conditions are shown in Figure 1. The material properties used are ($G_{12} = G_{13}$; $\nu_{12} = \nu_{13}$),

$$\text{Material I: } E_1/E_2 = 25, \quad G_{12}/E_2 = 0.5, \quad G_{23}/E_2 = 0.2, \quad \nu_{12} = 0.25.$$

$$\text{Material II: } E_1/E_2 = 40, \quad G_{12}/E_2 = 0.6, \quad G_{23}/E_2 = 0.5, \quad \nu_{12} = 0.25$$

A value of 5/6 was used for the shear correction coefficients (see Whitney^{4,2}).

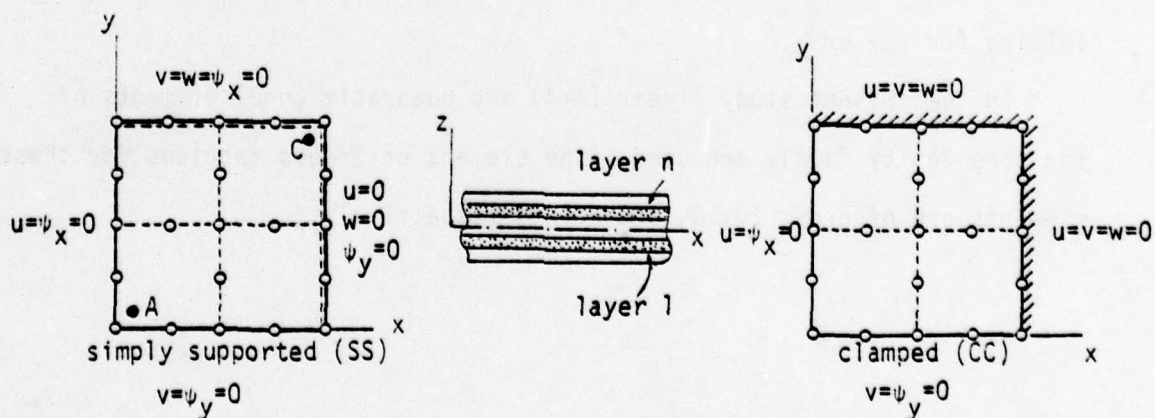


Figure 1 Coordinate system, finite-element mesh, and boundary conditions

Bending Analysis

First the effect of the reduced integration on the bending deflection and stresses is examined using a four-layer, cross-ply ($0^\circ/90^\circ/90^\circ/0^\circ$), simply supported square plate (Material II) subjected to sinusoidal loading (SSL),

$$P = P_0 \cos \frac{\pi X}{a} \cos \frac{\pi Y}{b}$$

The percentage error (between the solution obtained by using 2x2 Gauss points and 3x3 Gauss points) in the center deflection and maximum normal stress ($\bar{\sigma}_x = \bar{\sigma}_y$) as a function of the side-to-thickness ratio (a/h) are shown in Figure 2. The stresses were computed at the Gaussian points using equation (3). Figure 3 shows the bending deflection versus the side-to-thickness ratio for the same problem using 2x2 Gauss rule. This result is in excellent agreement with the closed-form solution of Whitney⁴³. Thus, the standard 3x3 Gauss rule (for the numerical integration of elements in equation (21)) gives less accurate results, especially for ratios $a/h > 10$. Guided by this observation (also, see Zienkiewicz et al.⁴⁰) the remaining results were obtained using 2x2 Gauss rule.

Figure 3 also shows the stresses, $\bar{\sigma}_x$, $\bar{\sigma}_y$, and $\bar{\tau}_{xy}$ for the four-layer, cross-ply ($0^\circ/90^\circ/90^\circ/0^\circ$), simply supported square plate under sinusoidal loading. To see the effect of loading and material on the deflection, the same problem was solved using Material II and uniform loading, and Material I and sinusoidal loading. Note that decreasing the ratio E_1/E_2 from 40 to 25 has the same effect as using the uniform loading in place of sinusoidal loading. Bending deflections and stresses are presented in Table 1 for a (4-ply ($0^\circ/90^\circ/90^\circ/0^\circ$), Material I) clamped plate under sinusoidal loading, and simply supported plate under point load at the center.

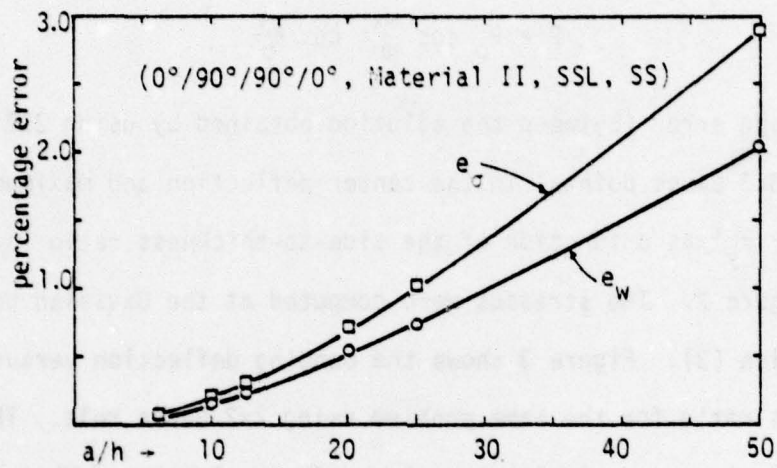


Figure 2 Effect of reduced integration on the bending deflections and stresses

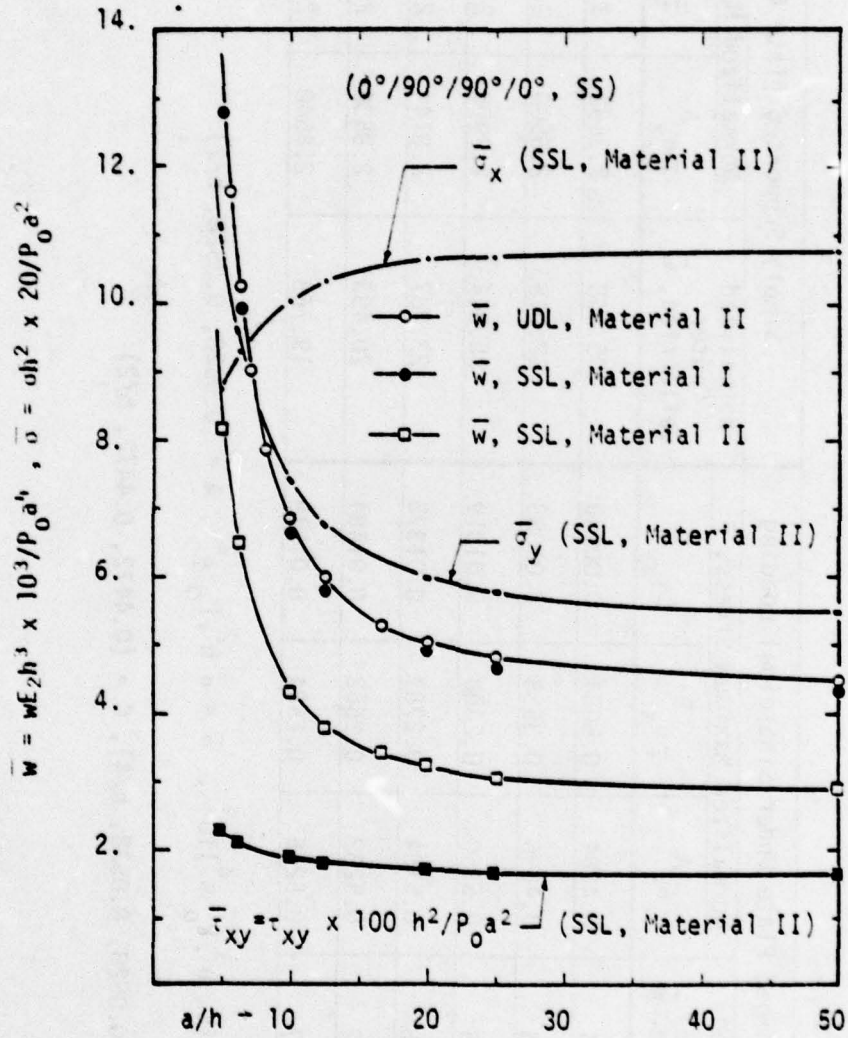


Figure 3 Bending deflections, and stresses vs. side to thickness ratio for four-layer, cross-ply, simply supported square plates

Table 1 Four-Layer (0°/90°/90°/0°) Square Plate (Material I)

a/h	Clamped Plate Under Sinusoidal Loading			Simply Supported Plate Under Point Load				
	Normalized Center Deflection, \bar{w}	Normalized Maximum Stress, $\bar{\sigma}$			Normalized Center Deflection, \bar{w}	Normalized Maximum Stress, $\bar{\sigma}$		
		$\mp \sigma_x$	$\mp \sigma_x$	$\pm \tau_{xy}$		$\mp \sigma_x$	$\mp \sigma_x$	$\pm \tau_{xy}$
5	12.9544	0.4284	0.5084	0.00900	105.448	2.3692	3.4564	0.0874
10	6.6956	0.4896	0.3538	0.01083	42.015	2.6500	2.7160	0.0765
20	4.9415	0.5150	0.2880	0.01319	25.344	2.7900	2.3258	0.0712
25	4.7208	0.5184	0.2787	0.01378	23.287	2.8144	2.2560	0.07029
50	4.4222	0.5232	0.2662	0.01484	20.493	2.8536	2.1296	0.06904
100	4.3567	0.5255	0.2634	0.01519	19.763	2.8640	2.0590	0.06916

$$\bar{w} = W(E_2 h^3 / P_0 a^4) 10^3, \quad \bar{\sigma} = \sigma h^2 / P_0 a^2, \quad A = (0.0528, 0.0528, h/2)$$

$$B = (0.0528, 0.0528, h/4), \quad C = (0.4472, 0.4472, h/2)$$

To further illustrate the accuracy of the present element, two problems for which exact^{5,7} and finite element solutions^{32,33} are available, were solved and results are summarized in Tables 2 and 3 (for Material I). Table 2 contains the normalized bending deflections and stresses for three-layer, cross-ply ($0^\circ/90^\circ/0^\circ$), simply supported square plate subjected to sinusoidal loading. The outer layers are each $h/4$, and the middle layer is $h/2$ thick (i.e. sandwich construction). Table 3 contains similar information for three-layer (equal thickness), cross-ply ($0^\circ/90^\circ/0^\circ$), simply supported rectangular ($b/a = 3$) plate under sinusoidal loading. Present solutions are compared with exact solutions of Pagano⁵ and Pagano and Hatfield⁷, and the finite-element solutions of Panda and Natarajan³² and Maweny and Davies³³. It is clear that the present solution is the closest to the exact solution for the deflection for all ratios of a/h . Since the stresses in the present study are computed at the Gaussian points, it is not meaningful to compare for relative accuracy.

Figure 4 shows the normalized bending deflections versus the ratio a/h for the 3-layer, cross-ply, simply supported square plate under sinusoidal loading. For Material I the same problem was resolved with layer orientation of $0^\circ/91^\circ/0^\circ$ (the middle layer is now oriented at 91°) to see the effect of slight variation (introduced, say, in manufacturing) in the orientation of the layers on the deflection. Note that the error in the angle causes slight variation in the deflection only at higher values of a/h (i.e. for thin plates).

Figure 5 shows plots of bending deflection versus the side-to-thickness ratio for two-layer, cross-ply ($0^\circ/90^\circ$) square plate (Material II) under sinusoidal and uniform loadings, and for four-layer, symmetric angle-ply

Table 2 Three-layer ($0^\circ/90^\circ/0^\circ$) simply supported square plate subjected to sinusoidal loading (Material I, $t_1 = t_3 = h/4$, $t_2 = h/2$)

a/h	Source	Normalized center deflection \bar{w}	Normal stresses, $\bar{\sigma}$ (top and bottom)*		
			$\mp \sigma_x(0,0,h/2)$	$\mp \sigma_y(0,0,h/4)$	$\pm \tau_{xy}(\frac{a}{2}, \frac{b}{2}, \frac{h}{2})$
5.0	Present FEM	2.9642	0.4196	0.5000	0.02804
6.25	Present FEM	2.2998	0.4442	0.4431	0.02629
10	Pagano & Hatfield ⁷	1.709	0.559	0.403	0.0276
	Present FEM	1.5340	0.4842	0.3509	0.02342
	Panda & Natarajan ³²	1.448	0.532	0.307	0.0250
	Mawenya & Davies ³³	2.034	0.542	--	0.0292
12.5	Present FEM	1.3465	0.4965	0.3223	0.02241
20	Pagano & Hatfield ⁷	1.189	0.543	0.309	0.0230
	Present FEM	1.1364	0.5118	0.2870	0.02144
	Panda & Natarajan ³²	1.114	0.557	0.307	0.0231
	Mawenya & Davies ³³	1.273	0.546	--	0.0239
25	Present FEM	1.0866	0.5154	0.2779	0.02115
50	Pagano & Hatfield ⁷	1.031	0.539	0.276	0.0216
	Present FEM	1.0197	0.5208	0.2656	0.02077
	Panda & Natarajan ³²	1.016	0.565	0.287	0.0225
	Mawenya & Davies ³³	1.048	0.550	--	0.0221
100	Pagano & Hatfield ⁷	1.008	0.539	0.271	0.0214
	Present FEM	1.0055	0.5235	0.2630	0.02073
	Panda & Natarajan ³²	1.003	0.566	0.284	0.0223
	Mawenya & Davies ³³	1.015	0.551	--	0.0213
Classical plate theory		1.000	0.539	0.269	0.0213

$$\bar{w} = w_\alpha(h^3/P_0 a^4), \quad \bar{\sigma} = \sigma h^2/P_0 a^2, \quad \alpha = \{4G_{12} + [E_1 + (1+\nu_{12})E_2]/(1-\nu_{12}\nu_{21})\} \pi^4/12$$

* Computed at the Gaussian points in the present study.

Table 3 Three-layer (0°/90°/0°) simply supported rectangular plate (b/a = 3) subjected to sinusoidal loading (Material I)

a/h	Source	Normalized center deflection, \bar{w}	Normalized stress, $\bar{\sigma}$ (top and bottom)*		
			$\mp \sigma_x(0,0,h/2)$	$\mp \sigma_y(0,0,h/6)$	$\pm \tau_{xy}(\frac{a}{2}, \frac{b}{2}, \frac{h}{2})$
5	Present FEM	1.695	0.5984	0.0691	0.01789
6.25	Present FEM	1.267	0.6006	0.0540	0.01338
10	Exact: Pagano ⁵	0.919	0.725	0.0435	0.0123
	Present FEM	0.802	0.6031	0.0364	0.01017
	Panda & Natarajan ³²	0.752	0.653	0.0367	0.0105
	Mawenya & Davies ³³	1.141	0.685	--	0.0141
12.5	Present FEM	0.694	0.6038	0.0322	0.00941
20	Exact: Pagano ⁵	0.610	0.650	0.0299	0.0093
	Present FEM	0.578	0.6045	0.0276	0.00858
	Panda & Natarajan ³²	0.565	0.654	0.0287	0.0091
	Mawenya & Davies ³³	0.664	0.651	--	0.0099
25	Present FEM	0.551	0.6046	0.0264	0.00838
50	Exact: Pagano ⁵	0.520	0.628	0.0259	0.0084
	Present FEM	0.515	0.6044	0.0251	0.00812
	Panda & Natarajan ³²	0.513	0.654	0.0264	0.0087
	Mawenya & Davies ³³	0.529	0.640	--	0.0087
100	Exact: Pagano ⁵	0.508	0.624	0.0253	0.0083
	Present FEM	0.506	0.6034	0.0253	0.00802
	Panda & Natarajan ³²	0.505	0.654	0.0261	0.0086
	Mawenya & Davies ³³	0.510	0.638	--	0.0085
Classical plate theory		0.503	0.623	0.0252	0.0083

$$\bar{w} = w \cdot 100 E_2 h^3 / P_0 a^4, \quad \bar{\sigma} = \sigma h^2 / P_0 a^2$$

* Computed at the Gaussian points in the present study.

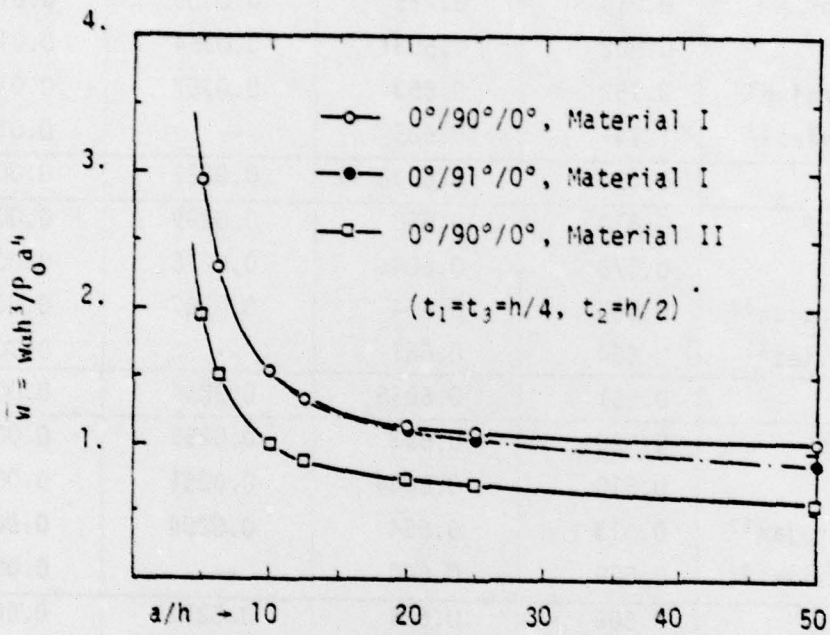


Figure 4 Bending deflection vs. side-to-thickness ratio for 3-layer, cross-ply, simply supported square plate under sinusoidal loading

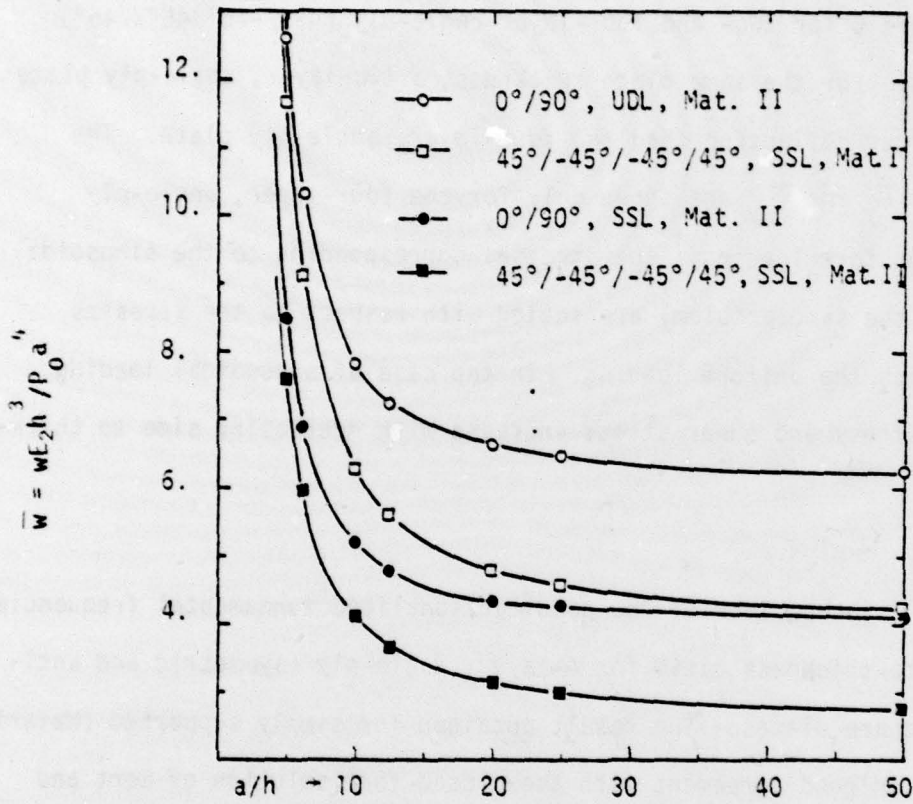



Figure 5 Bending deflections vs. side-to-thickness ratio for two-layer cross-ply ($0^\circ/90^\circ$) and four-layer, angle-ply, simply supported square plate

(45°/-45°/-45°/45°) square plate (Material I and II) under sinusoidal loading. It is clear that the effect of shear deformation is quite significant in (cross-ply, as well as angle-ply) composites with side-to-thickness ratio, $a/h < 20$.


Bending deflections and stresses versus side-to-thickness ratio are shown in Figure 6 for two- and four-layer angle-ply (45°/-45°/45°//45°) square plates. For the same plate thickness, a two-layer, angle-ply plate undergoes larger deflection than the four-layer, angle-ply plate. The stresses $\bar{\sigma}_x = \bar{\sigma}_y$ and $\bar{\tau}_{xy}$ are shown only for the four-layer, angle-ply plate under uniform loading. The stresses corresponding to the sinusoidal loading (for the same problem) are scaled with respect to the stresses associated with the uniform loading. In the case of sinusoidal loading both normal stress and shear stress increase with decreasing side to thickness ratio.

Free vibration analysis

Figure 7 shows plots of the nondimensionalized fundamental frequencies versus side-to-thickness ratio for 4-layer, angle-ply (symmetric and antisymmetric) square plates. The result obtained for simply supported (Material II) plate is in good agreement with the closed-form solution of Bert and Chen²³. The present study predicts higher frequencies, with the deviation increasing with a/h . Figure 7 also shows the plot of fundamental frequencies for the symmetric angle-ply (45°/-45°/-45°/45°, Material I). Incidentally, this plot is in excellent agreement with that in Figure 5 of Whitney and Pagano²⁰. However, the figure caption there (i.e. in reference 20) says that the result was obtained for four-layer, antisymmetric angle-ply (45°/-45°/45°/-45°), simply-supported square plate (Material II). As pointed

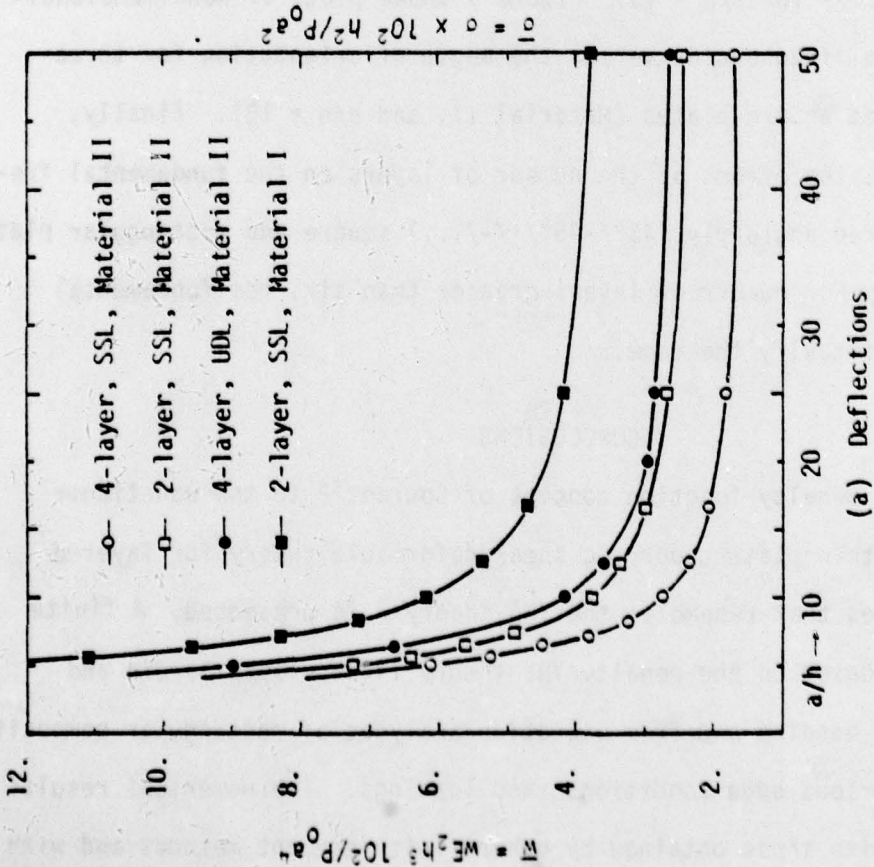

(a) Deflections

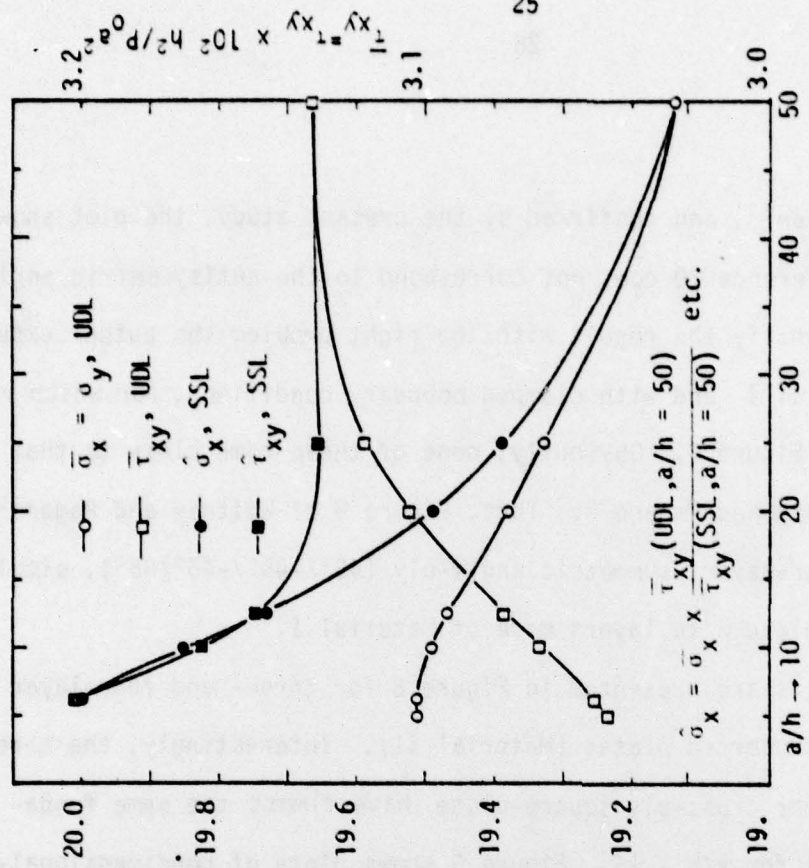

(b) Stresses (4-layer, Material II)

Figure 6 Bending deflections and stresses vs. side-to-thickness ratio for angle-ply, simply supported square plates

out by Bert and Chen²³, and confirmed by the present study, the plot shown in Figure 5 of Reference 20 does not correspond to the antisymmetric angle-ply plate. To identify the result with the right problem the author experimented with Material I and with clamped boundary conditions, for which results are also shown in Figure 7. Obviously, none of these come close to that presented by Whitney and Pagano²⁰. Thus, Figure 5 of Whitney and Pagano²⁰ corresponds to four-layer, symmetric angle-ply ($45^\circ/-45^\circ/-45^\circ/45^\circ$), simply supported square plate with layers made of Material I.

Similar results are presented in Figure 8 for three- and four-layer cross-ply simply supported plates (Material II). Interestingly, the three-layer and four-layer cross-ply square plate have almost the same fundamental frequencies for $a/h < 15$. Figure 9 shows plots of nondimensionalized fundamental frequencies versus the angle of orientation for three- and four-layered square plates (Material II, and $a/h = 10$). Finally, Figure 10 shows the effect of the number of layers on the fundamental frequency of layered angle-ply ($45^\circ/-45^\circ/+/-/\dots$) square and rectangular plates (Material II). For number of layers greater than six, the fundamental frequency is virtually the same.

CONCLUSIONS

Using the penalty function concept of Courant³⁵ to the equations governing the thin-plate theory, a shear deformable theory for layered composite plates that resembles the YNS theory¹² is presented. A finite element model based on the penalty/YNS theory is developed herein and applied to the bending and free vibration analyses of rectangular composite plates with various edge conditions and loadings. The numerical results are compared with those obtained by other finite-element methods and with

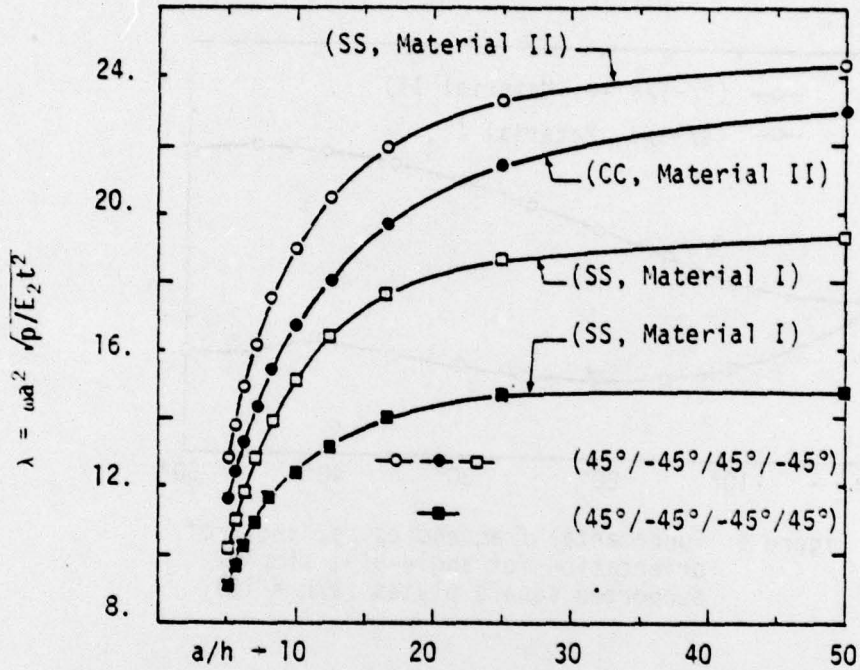


Figure 7 Fundamental frequencies vs. side-to-thickness ratio for 4-layer, angle-ply square plates

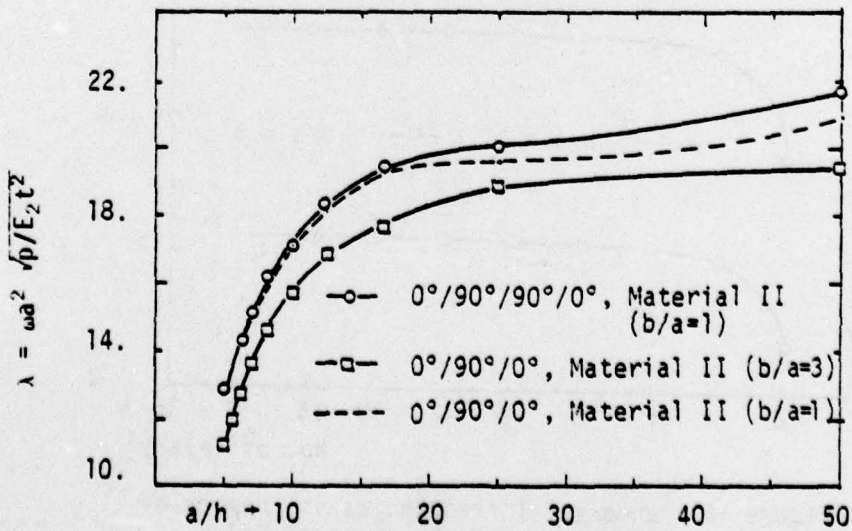


Figure 8 Fundamental frequencies vs. side-to-thickness ratio for cross-ply plates

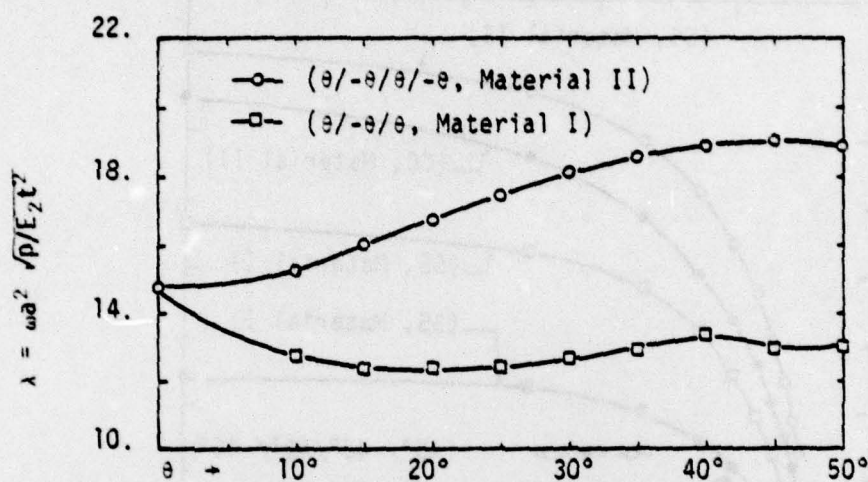


Figure 9 Fundamental frequencies vs. angle of orientation for angle-ply, simply supported square plates ($a/h = 10$)

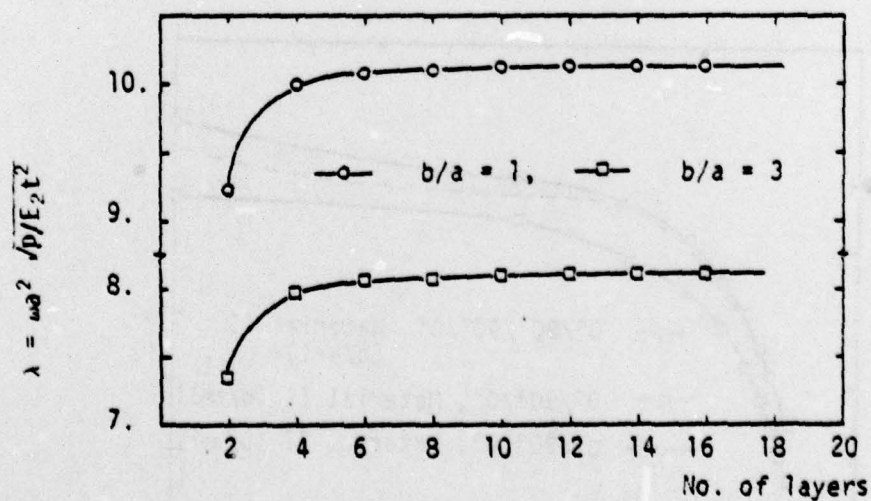


Figure 10 Fundamental frequencies vs. number of layers for four-layer, angle-ply ($45^\circ/-45^\circ/45^\circ/-45^\circ$), simply supported plate ($a/h = 10$, Material II)

exact solutions. The present element, despite its simplicity in formulation and programming, gives the most accurate results.

Application of the element to nonlinear (in von Karman sense) and bimodulus (i.e. different elastic properties in tension and compression) plate problems was investigated recently by the author^{44,45}. However, its application to a nonlinear, shear deformable theory of composite plates is still awaiting.

Acknowledgements

Support of this work by the Office of Naval Research through Contract N00014 78-C-0647 is gratefully acknowledged. The author is also thankful to his colleague, Dr. C. W. Bert, for many helpful comments.

APPENDIX

A_{ij}, B_{ij}, D_{ij} = extensional, flexural-extensional, and flexural stiffnesses
($i, j=1, 2, 6$)

a, b = plate planform dimensions in x, y directions

E_1, E_2 = layer elastic moduli in directions along fibers and normal to them, respectively

F_i = force components in the finite element formulation ($i=1, 2, \dots, 5$)

G_{12}, G_{13}, G_{23} = layer in-plane and thickness shear moduli

h = total thickness of plate

I = rotary inertia coefficient per unit midplane area of lamina

k_i = shear correction coefficients associated with the yz and xz planes, respectively ($i=1, 2$)

$K_{ij}^{\alpha\beta}$ = element stiffness coefficients ($i, j=1, 2, \dots, 80$; $\alpha, \beta=1, 2, \dots, 5$)

L = total number of layers in the plate

M_i, N_i = stress couple, and stress resultant, respectively ($i=1, 2, 6$)

M_{ij}^e = element mass coefficients ($i, j=1, 2, \dots, 8$)

N_i^e = element shape functions ($i=1, 2, \dots, 8$)

- n = nodes per element
 p = laminate normal inertia coefficient per unit midplane area
 P = transversely distributed load
 P_0 = intensity of transversely distributed load
 Q_x, Q_y = shear stress resultants
 Q_{ij} = plane stress reduced stiffness coefficients ($i, j=1, 2, 6$)
 R = laminate rotary-normal coupling inertia coefficient per unit midplane area
 $S_{ij}^{\xi\eta}$ = element matrices in FEM formulation ($i, j=1, 2, \dots, 8$; $\xi, \eta=0, x, y$)
 t = time
 u, v, w = displacement components in x, y, z directions, respectively
 u_0, v_0 = in-plane displacements in x, y directions
 u_i, v_i = nodal values of displacements u, v ($i=1, 2, \dots, 8$)
 U, U_1, U_2, U_L = strain energies
 V = potential energy
 x, y, z = position coordinates in cartesian system
 $\gamma_{xy}, \gamma_{xz}, \gamma_{yz}$ = shear strains
 $\{\Delta\}$ = column of vector of generalized nodal displacements
 ϵ_i = penalty parameters ($i=1, 2$)
 $\epsilon_x, \epsilon_y, \epsilon_z$ = normal strains
 θ_m = orientation of m -th laminate ($m=1, 2, \dots, L$)
 λ_x, λ_y = Lagrange multipliers
 π, π_p = total potential energy functionals
 $\sigma_x, \sigma_y, \sigma_z$ = normal stresses
 $\tau_{xy}, \tau_{xz}, \tau_{yz}$ = shear stresses
 ψ_x, ψ_y = slope functions
 ω = fundamental frequency of free vibration

REFERENCES

1. R. D. Mindlin, 'Influence of Rotary Inertia and Shear on Flexural Motions of Isotropic, Elastic Plates', J. Appl. Mech. 18, 31-38 (1951).
2. E. Reissner, 'On Transverse Bending of Plates, Including the Effect of Transverse Shear Deformation', Int. J. Solids and Structures, 11, 569-573 (1975).
3. K. H. Lo, R. M. Christensen, and E. M. Wu, 'A Higher-Order Theory of Plate Deformation Part 1: Homogeneous Plates, Part 2: Laminated Plates', J. Appl. Mech., 44, 662-668, 669-676 (1977).
4. N. J. Pagano, 'Exact Solutions for Composite Laminates in Cylindrical Bending', J. of Composite Materials, 3(3), 398-411 (1969).
5. N. J. Pagano, 'Exact Solutions for Rectangular Bidirectional Composites and Sandwich Plates', J. of Composite Materials, 4, 20-34 (1970).
6. N. J. Pagano and S. D. Wang, 'Further Study of Composite Laminates Under Cylindrical Bending', J. of Composite Materials, 5, 521-528 (1971).
7. N. J. Pagano and S. J. Hatfield, 'Elastic Behavior of Multilayer Bidirectional Composites', AIAA Journal, 10, 931-933 (1972).
8. E. Reissner and Y. Stavsky, 'Bending and Stretching of Certain Types of Heterogeneous Anisotropic Elastic Plates', J. of Appl. Mech. 28, 402-408 (1961).
9. S. B. Dong, K. S. Pister, and R. L. Taylor, 'On the Theory of Laminated Anisotropic Shells and Plates', J. Aerospace Sciences, 29, 969-975 (1962).
10. C. W. Bert and B. L. Mayberry, 'Free Vibrations of Unsymmetrically Laminated Anisotropic Plate with Clamped Edges', J. Composite Materials, 3, pp. 282-293 (1969).
11. Y. Stavsky, 'On the Theory of Symmetrically Heterogeneous Plates Having the Same Thickness Variation of the Elastic Moduli', Topics in Appl. Mech., 105, D. Abir, F. Ollendorff, and M. Reiner (eds.) American Elsevier, New York (1965).
12. P. C. Yang, C. H. Norris, and Y. Stavsky, 'Elastic Wave Propagation in Heterogeneous Plates', Int. J. Solids and Structures, 2, 665-684 (1966).
13. C. T. Sun and J. M. Whitney, 'Theories for the Dynamic Response of Laminated Plates', AIAA J. 11, 178-183 (1973).
14. J. M. Whitney and C. T. Sun, 'A Higher Order Theory for Extensional Motion of Laminated Composites', J. Sound and Vibration, 30, 85-97 (1973).

15. S. Srinivas and A. K. Rao, 'Bending, Vibration, and Buckling of Simply Supported Thick Orthotropic Rectangular Plates and Laminates', Int. J. Solids and Structures, 6, 1463-1481 (1970).
16. C. W. Bert, 'Analysis of Plates', Structural Design and Analysis, Part I, C. C. Chamis (ed.), Academic Press, New York (1974).
17. S. T. Mau, 'A Refined Laminated Plate Theory', J. Appl. Mech. 40, 606-607 (1973).
18. C. T. Sun, J. D. Achenback, G. Herrmann, 'Continuum Theory for a Laminated Medium', J. Appl. Mech. 35, 467-475 (1968).
19. A. Bedford and M. Stern, 'Toward a Diffusing Continuum Theory of Composite Materials', J. Appl. Mech. 38, 8-14 (1971).
20. J. M. Whitney and N. J. Pagano, 'Shear Deformation in Heterogeneous Anisotropic Plates', J. Appl. Mech. 37, 1031-1036 (1970).
21. R. C. Fortier and J. N. Rossettos, 'On the Vibration of Shear Deformable Curved Anisotropic Composite Plates', J. Appl. Mech. 40, 299-301 (1973).
22. P. K. Sinha and A. K. Rath, 'Vibration and Buckling of Cross-Ply Laminated Circular Cylindrical Panels', Aeronautical Quarterly, 26, 211-218 (1975).
23. C. W. Bert and T. L. C. Chen, 'Effect of Shear Deformation on Vibration of Antisymmetric Angle-Ply Laminated Rectangular Plates', Int. J. Solids and Structures, 14, 465-473 (1978).
24. C. W. Pryor Jr. and R. M. Barker, 'A Finite Element Analysis Including Transverse Shear Effects for Applications to Laminated Plates', AIAA J. 9, 912-917 (1971).
25. R. M. Barker, F. T. Lin, and J. R. Dara, 'Three-Dimensional Finite-Element Analysis of Laminated Composites', National Symposium on Computerized Structural Analysis and Design, George Washington University (1972).
26. A. K. Noor and M. D. Mathers, 'Shear-Flexible Finite Element Models of Laminated Composite Plates and Shells', NASA TN D-8044 (1975).
27. A. K. Noor and M. D. Mathers, 'Anisotropy and Shear Deformation in Laminated Composite Plates', AIAA J. 14, 282-285 (1976).
28. A. K. Noor and M. D. Mathers, 'Finite Element Analysis of Anisotropic Plates', Int. J. Num. Meth. Engng. 11, 289-307 (1977).
29. S. T. Mau and E. A. Witmer, 'Static, Vibration, and Thermal Stress Analyses of Laminated Plates and Shells by the Hybrid-Stress Finite Element Method with Transverse Shear Deformation Effects Included', Aeroelastic and Structures Research Laboratory, Report ASRL TR 169-2, Department of Aeronautics and Astronautics, MIT, Cambridge, MA (1972).
30. S. T. Mau, P. Tong, and T. H. H. Pian, 'Finite Element Solutions for Laminated Thick Plates', J. Composite Materials, 6, 304-311 (1972).

31. R. H. Gallagher, 'Significant Advances in Finite Elements Over the Last Three Years', Proc. Conf. on Mathematics of Finite Elements and Applications III, Brunel University, Uxbridge, England (1978).
32. S. C. Panda and R. Natarajan, 'Finite Element Analysis of Laminated Composite Plates', Int. J. Num. Meth. Engng. 14, 69-79 (1979).
33. A. S. Mawenya and J. D. Davies, 'Finite Element Bending Analysis of Multilayer Plates', Int. J. Num. Meth. Engng. 8, 215-225 (1974).
34. S. Ahmad, B. M. Irons, and O. C. Zienkiewicz, 'Analysis of Thick and Thin Shell Structures by Curved Finite Elements', Int. J. Num. Meth. Engng. 2, 419-451 (1970).
35. R. Courant, Calculus of Variations and Supplementary Notes and Exercise, revised and amended by J. Moser, New York University (1956).
36. O. C. Zienkiewicz, 'Constrained Variational Principles and Penalty Analysis Function Methods in Finite Elements', Conf. on Numer. Solution of Differential Equation, Dundee, Lecture Notes on Mathematics, Springer-Verlag, (1973).
37. G. Wempner, J. T. Oden, and D. A. Kross, 'Finite Element Analysis of Thin Shells', Proc. ASCE, J. Engng. Mech. Div. 95, 1273-1294 (1968).
38. I. Fried, 'Shear in C^0 and C^1 Plate Bending Elements', Int. J. Solids and Structures, 9, 449-460 (1973).
39. I. Fried, 'Residual Energy Balancing Technique in the Generation of Plate Bending Finite Elements', Computers and Structures, 4, 771-778 (1974).
40. O. C. Zienkiewicz, R. L. Taylor, and J. M. Too, 'Reduced Integration Technique in General Analysis of Plates and Shells', Int. J. Num. Meth. Engng. 3, 575-586 (1971).
41. T. J. R. Hughes, R. L. Taylor, and W. Kanoknukulchai, 'A Simple and Efficient Finite Element for Plate Bending', Int. J. Num. Meth. Engng. 11, 1529-1543 (1977).
42. J. M. Whitney, 'Stress Analysis of Thick Laminated Composite and Sandwich Plates', J. Composite Materials, 6, 426-440 (1972).
43. J. M. Whitney, 'The Effect of Transverse Shear Deformation on the Bending of Laminated Plates', J. Composite Materials, 3, 534-547 (1969).
44. J. N. Reddy, 'Simple Finite Elements with Relaxed Continuity for Non-linear Analysis of Plates', Proc. Third International Conf. in Australia on Finite Element Methods, University of New South Wales, Sydney, July 2-6, 1979.
45. J. N. Reddy, and C. W. Bert, 'Analysis of Plates Constructed of Fiber-Reinforced Bimodulus Composite Material', in Mechanics of Bimodulus Materials, C. W. Bert (ed.), ASME Winter Annual Meeting, New York (1979), to appear.