

AD-A107 714


NAVAL RESEARCH LAB WASHINGTON DC LAB FOR THE STRUCTU--ETC F/G 7/4
NEW ENERGETIC MATERIALS - STRUCTURAL CHARACTERIZATION.(U)
OCT 81 R GILARDI, C F GEORGE, J KARLE

UNCLASSIFIED

LSM-81-1

NL

1 of 1
AD
A107714

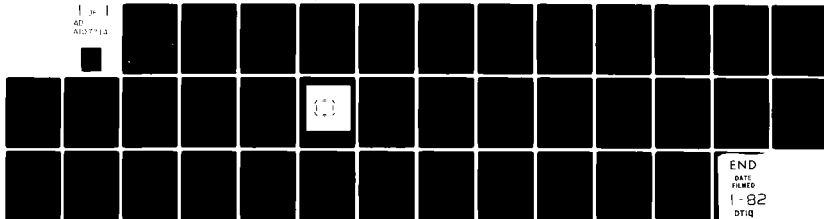

END
DATE
FILMED
1-82
DTIC

AD A107714

MIC FILE COPY

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER LSM-81-1	2. GOVT ACCESSION NO. AD-A107714	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) New Energetic Materials - Structural Characterization		5. TYPE OF REPORT & PERIOD COVERED Annual Report, 10/1/80-9/30/81
6. AUTHOR(s) R. Gilardi, C. F. George, Jr., Karle		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Laboratory for the Structure of Matter Naval Research Laboratory Washington, D. C. 20375		8. CONTRACT OR GRANT NUMBER(s) N0001481 WR10127 (011A6)
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE October 15, 1981
LEVEL II		13. NUMBER OF PAGES 27
		15. SECURITY CLASS. (this report) UNCLASSIFIED
15a. DECLASSIFICATION/DOWNGRADING SCHEDULE		
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Propellants, Elastomers, Explosives, X-ray Diffraction, Electron Diffraction		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The molecular structures of five new materials developed in ONR-sponsored explosive/propellant research are reported. The material 3,3-bis-azidomethyl oxetane (BAMO) was studied in three different forms. Using gas electron diffraction analysis, the molecular structure of the monomer of BAMO in the vapor phase was determined. A cyclic tetramer of BAMO was characterized with X-ray single-crystal diffraction analysis. (CONT'D)		

DD FORM 1473
1 JAN 73EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-014-6601

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

Finally, a linear polymer of BAMO was studied as a semi-crystalline fiber using x-rays. Most of the features of the polymer molecular structure were determined from the fiber diffraction pattern.

The crystal and molecular structure of a tetra-nitro compound, 4,7-bis-dinitrofluoromethyl-1,3-dioxepane, is reported; this compound is a newly synthesized monomer developed during research on the synthesis of nitro-polymers. The crystal and molecular structure of bis(5-amino-1,2,4-oxadiazole) is also reported. It is an unusually stable synthetic intermediate obtained in research aimed at producing new types of high-density nitro-explosives.

Accession For	
NTIS	☒
DTIC	☐
AD	☐
AN	☐
AS	☐
AW	☐
DA	☐
DD	☐
DE	☐
DF	☐
DR	☐
DS	☐
DT	☐
DU	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	☐
EO	☐
EP	☐
EQ	☐
ER	☐
ES	☐
ET	☐
EU	☐
EV	☐
EW	☐
EX	☐
EY	☐
EA	☐
EB	☐
EC	☐
ED	☐
EE	☐
EF	☐
EG	☐
EH	☐
EI	☐
EJ	☐
EK	☐
EL	☐
EM	☐
EN	

Office of Naval Research

Progress Report

New Energetic Materials -
Structural Characterization

Covering the period
Oct. 1, 1980 - Sept. 30, 1981

sponsored by the
Energetic Materials Research Program

Investigators: Dr. Richard Gilardi
Dr. Clifford George
Dr. Jerome Karle

Laboratory for the
Structure of Matter
Naval Research Laboratory
Washington, D. C. 20375

81 11 23 080

CONTENTS

- I. Introduction
 - II. The Electron Diffraction Analysis of 3,3-bis-azidomethyloxetane (BAMO)
 - III. The Crystal Structure of a Cyclic BAMO Tetramer
 - IV. The Crystal and Molecular Structure of the Energetic Polymer, (BAMO)_n
 - V. The Crystal Structure of a Tetranitrodifluoro Monomer: 4,7-bis(Dinitrofluoromethyl)-1,3-dioxepane
 - VI. The Crystal Structure of a Diaminodioxadiazole, a Synthetic Intermediate Originating in Research on the Synthesis of New High Explosives
 - VII. References
- Distribution List

I. Introduction

This report primarily concerns structural studies on three forms of BAMO, which is an apt acronym for the energetic compound, 3,3-bis-azidomethyl oxetane. Although we have experienced minor explosions with two of these materials, the monomer and the polymer, when working with them at elevated temperatures, all are stable at room temperature.

The BAMO polymer is an elastic white solid with moderate tendencies toward crystallinity. It is currently being manufactured, on a trial basis, for use as an elastic stabilizer for solid mixtures of fuels or explosives. It is insensitive to shock and resistant to accidental ignition, but decomposes rapidly at higher temperatures and thus contributes to the energy of the fuel or explosive.

The cyclic tetramer of BAMO is a by-product produced during polymerization. It can be crystallized as clear colorless prisms which showed no tendency to explode or deteriorate when irradiated with x-rays.

The monomer is a low-vapor-pressure liquid at room temperature which rapidly decomposes at higher temperatures (160-170°C). It was studied in the vapor state by gas electron diffraction analysis.

In addition, the report includes brief summaries of single-crystal diffraction structure determinations of two synthetic intermediates produced in ONR sponsored synthetic research on energetic nitro compounds at the Naval Surface Weapons Center and at the Lawrence Livermore Lab.

II. The Electron Diffraction Analysis of 3,3-bis-azidomethyloxetane (BAMO)

The samples of the monomer were provided by Dr. Kurt Baum of Fluorochem Inc. with a stated purity of 99.5% as determined by NMR. The scattering data were collected on the NRL gas electron diffraction apparatus using the sector-microphotometer method, and covered the range 1.95 to 31.45 s, where $s = (4\pi/\lambda) \sin(\theta/2)$. Here λ is the electron wavelength and θ is the angle the scattered electron beam makes with respect to the incident electron beam. The temperature of the gas injection system was maintained at 120°C during the data collection.

A least squares analysis of the experimental molecular intensity data converges for a model whose geometric parameters are listed in Table (1). The experimental molecular intensity curve and the difference curve, expt.-theo., are shown in Fig. (1). In the course of the analysis the possibility was considered that the vapor phase of the monomer could exist in a number of different conformers at room temperature. The model which best fit the experimental data, however, represents the single conformer shown in Fig. (2). This model has C_2 symmetry. It was computed on the basis that all C-H bond lengths are equal, all H-C-H angles are 110°, all C-C bond lengths are equal, and the N-N-N angle is 180°. In addition, the C-N distance was fixed at 1.46 Å, the average value of this bond length determined from the x-ray diffraction analysis of the crystalline tetramer of BAMO. A shrinkage correction

of 0.005 Å was made for the nonbonded N...N distance in each azido group as well as for the nonbonded C...C and C...O distances in the oxetane ring. The 87 distinct interatomic distances in the model make for a considerable overlap of contributors to the peaks in the radial distribution function, Fig. (3), making it rather unfeasible to determine from the experiment the vibrational amplitudes, l_{ij} , for the nonbonded distances. The l_{ij} values used to perform the calculations for Figs. (1 & 3) have been computed from approximate force constants.

The overall fit of the model to the experimental data is quite satisfactory as seen in Figs. (1 & 3), although the possibility of the presence of additional conformers in small amounts, as well as the presence of some thermal decomposition products cannot be ruled out. Additional analysis of the data is underway to refine the values of the structural parameters and to estimate the possible deviations from ideal values for bonds and angles used in the model calculations.


Table 1. Geometric parameters for 3,3-bis-azidomethyloxetane

	r_a (Å)	l_{ij} (Å)	Angle (deg.)
C-H	1.11	0.08	
N ₇ -N ₈	1.14	0.04	
N ₈ -N ₉	1.23	0.04	
C-O	1.47	0.06	
*C-N	1.46	0.05	
C-C	1.54	0.05	
C-C-C			88.5°
C ₅ -C ₁ -C ₆			107.5°
C ₁ -C ₅ -N ₇			111°
C ₅ -N ₇ -N ₈			126.5°
*H-C-H			110°
a) tau			65°
b) omega			90°
c) mu			0°

*assumed

- a) Torsion angle of the methyl groups about the C-C bond
- b) Torsion angle of the azido group about the C-N bond
- c) Angle representing ring pucker in the oxetane ring,
dihedral angle C₂-C₁-C₃-O₄

Fig. (1) Experimental molecular intensity curve for BAMO multiplied by s and the difference curve experimental - theoretical.

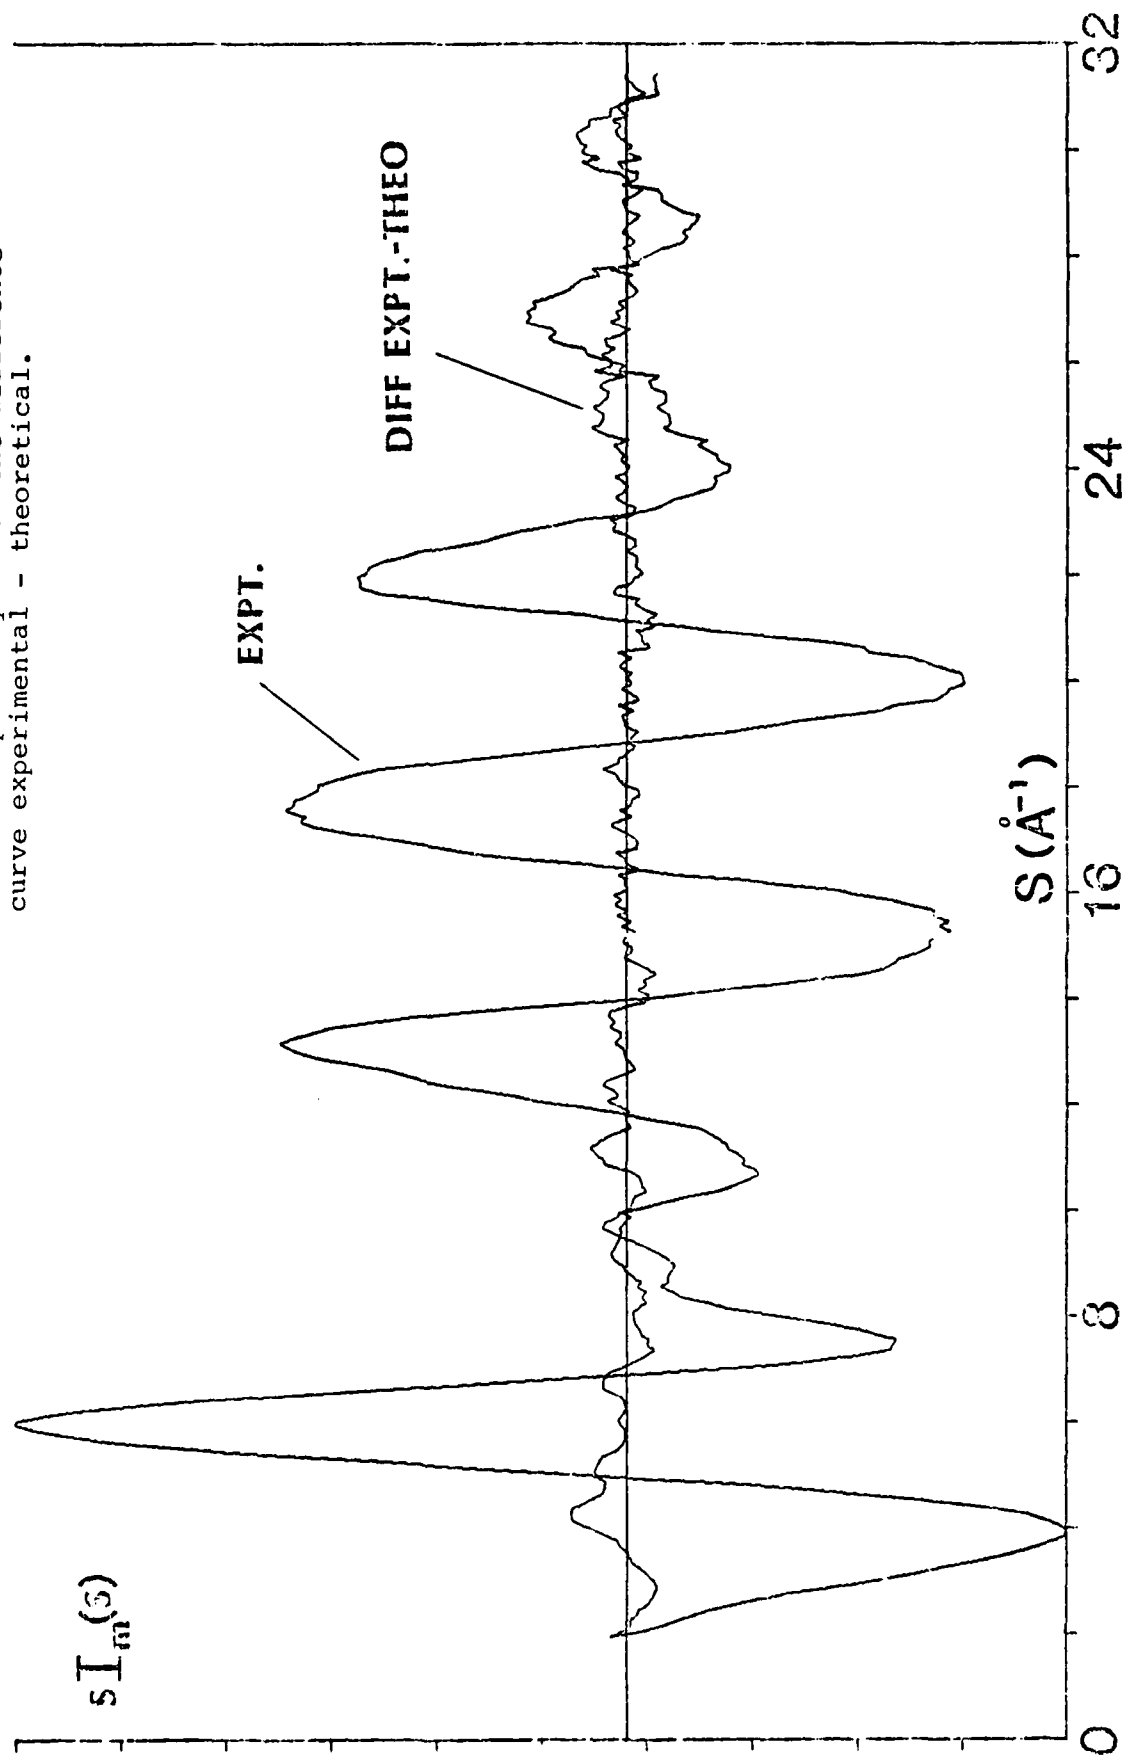

BAMO


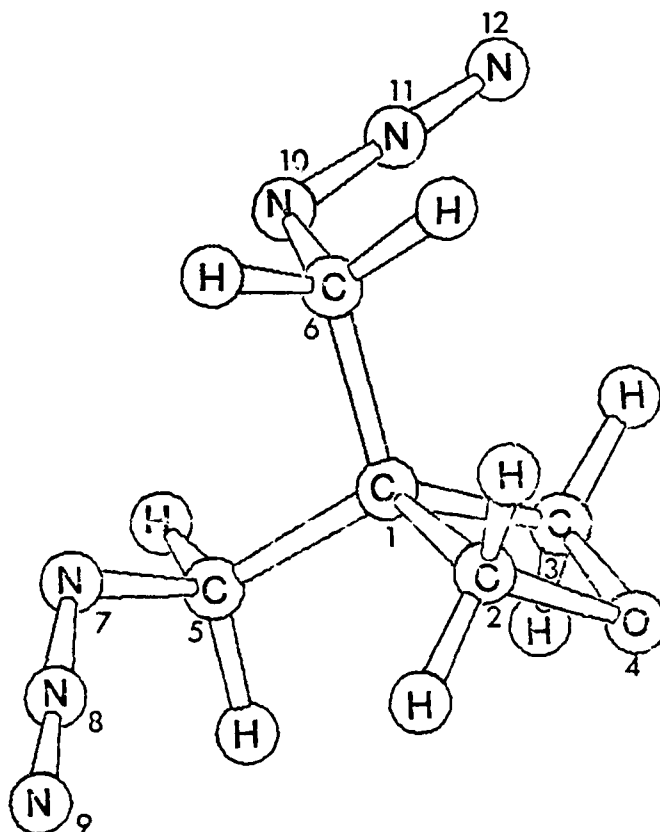


Fig. (2) Computer drawn model of BAMO representing the conformer which fits the experimental diffraction data.

Fig. (3) The observed radial distribution and difference curves for 3,3-bis-azidomethyloxetane.

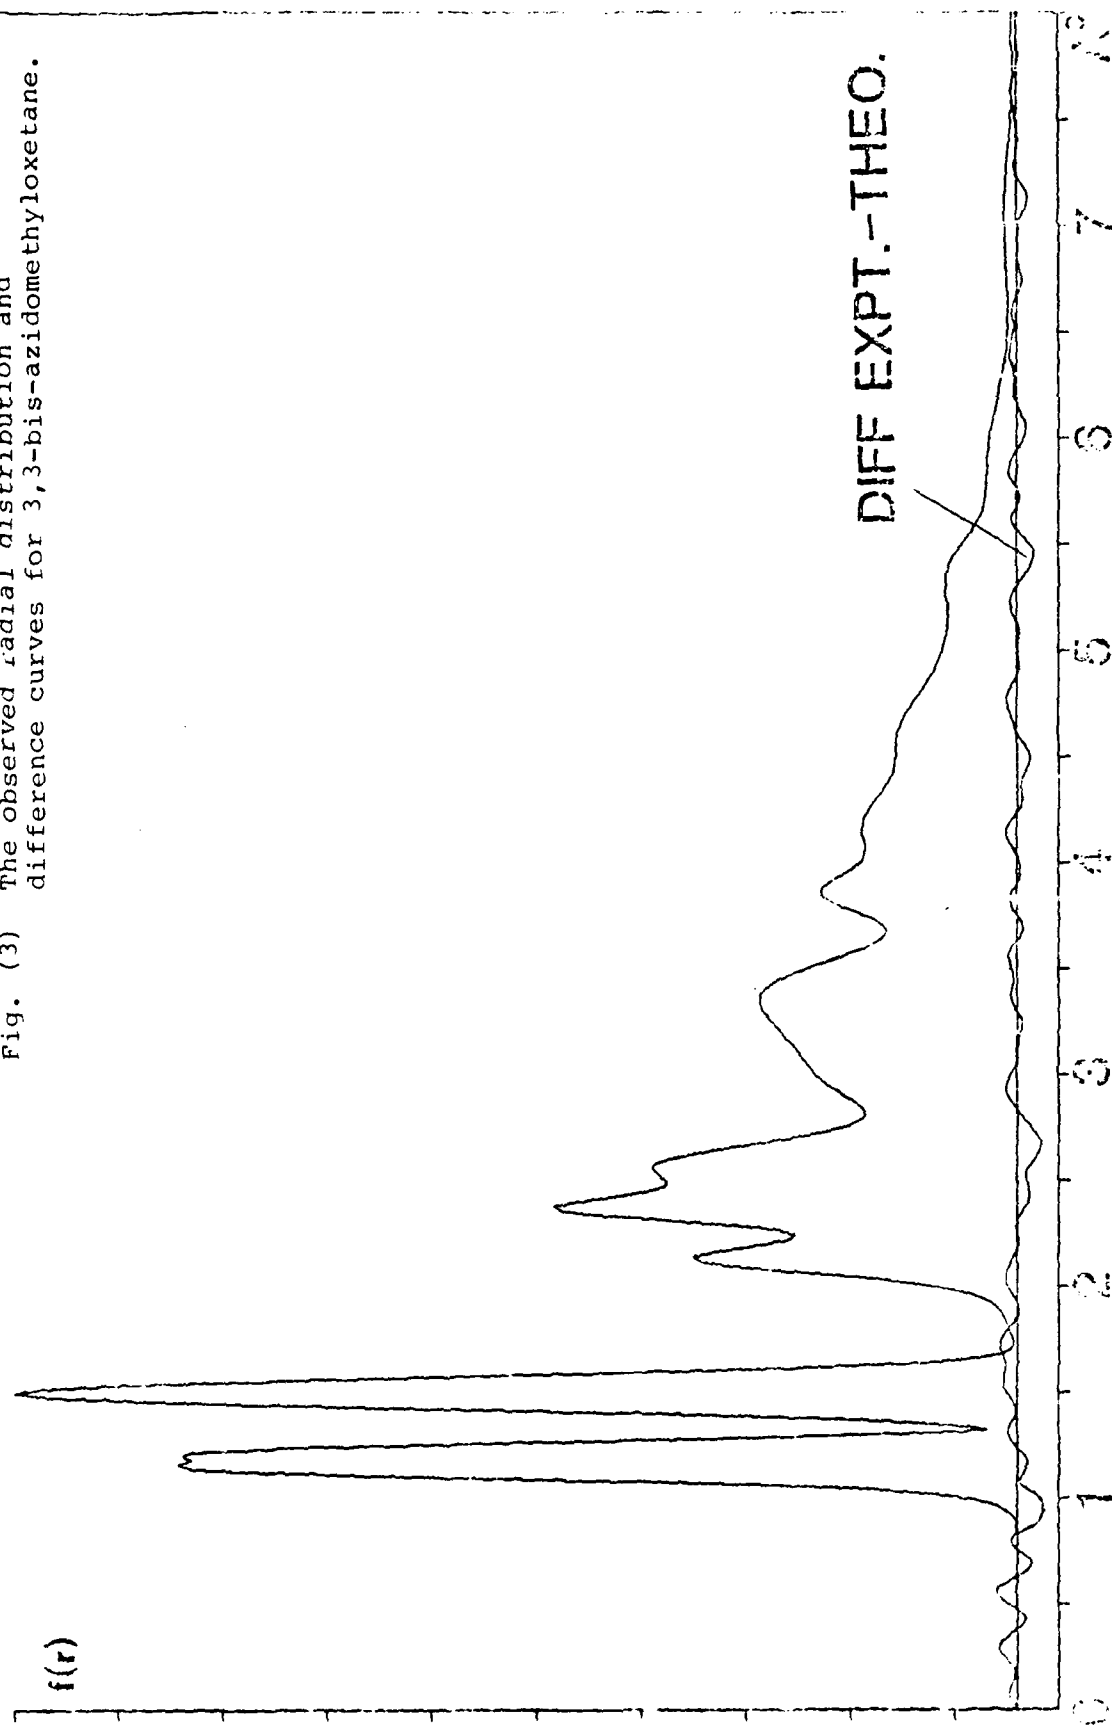

III. The Crystal Structure of a Cyclic BAMO Tetramer

Oligomers of BAMO may be formed as side products during the course of a polymerization reaction. A crystalline compound was leached from one of the samples of polymeric BAMO provided to us by soaking it in chloroform. This chloroform extract was evaporated and very small crystals (linear dimensions 0.05-0.20 mm.) were formed. At that time, the composition of this side product was unknown, but x-ray diffraction analysis was initiated, assuming the empirical formula would be similar to some multiple of BAMO.

The crystal space group symmetry is $Pbcn$, orthorhombic, with $a = 12.07$, $b = 15.22$, and $c = 18.18 \text{ \AA}$. The crystal and molecular structure were obtained by using the symbolic addition procedure (Karle and Karle, 1966). As indicated by the title of this section, the molecule is a tetramer of BAMO and thus contains eight methylazido side-chains. In the crystal, the molecule displays only 2-fold symmetry; the left and right halves of the molecule, shown in Fig. 4, are identical. However, the four independent methylazido groups in one half-molecule differ in their conformations, and this indicates that these regions of the molecule are inherently flexible, i.e., in solutions, each methylazido arm can probably shift easily from one conformation to another. In addition, weak "disorder" peaks are visible in the electron density maps near two of the azido side-chains. This indicates that a dynamic libration between alternative energetic minima is occurring to some extent, even in the solid state.

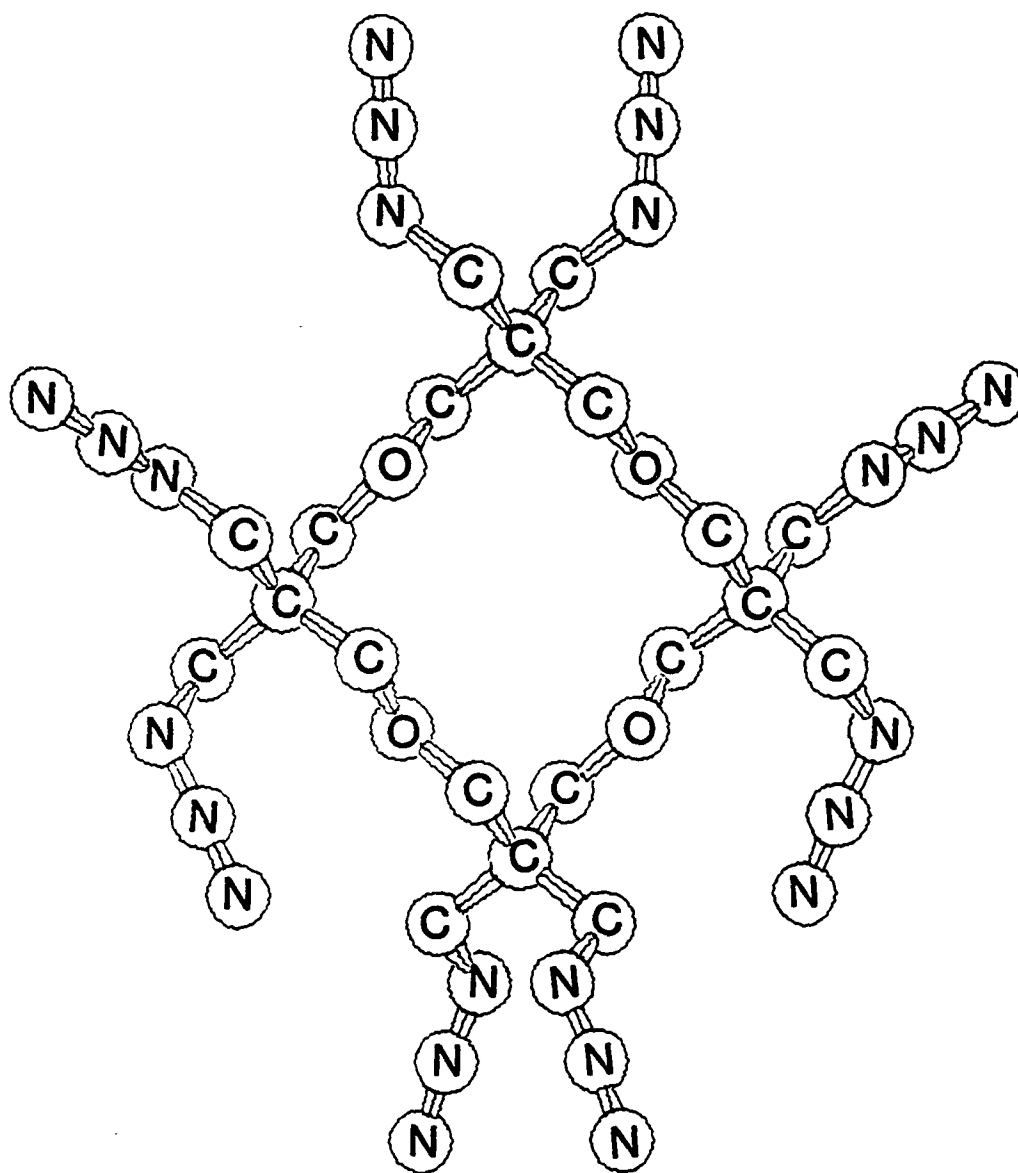


Fig. (4) The molecular structure of cyclic (BAMO)₄. Left and right halves of the molecule are identical in the crystal, related by a vertical two-fold axis.

The bond distances and angles determined for the tetramer (Table 2) provide realistic estimates for the bond distances and angles for the BAMO polymer. The large sixteen-membered ring of the cyclic tetramer contains four planar zig-zag "polyether" segments which are exactly analogous to the backbone linkages in $(\text{BAMO})_n$. The polymer diffraction analysis relies, in its intermediate stages, upon energetic calculations on a segmented polymer model, and these calculations are more likely to be correct if the model is based on a well-characterized small-molecule analog, such as, in this case, the BAMO tetramer.

Table 2. Bond Distances and Angles Obtained for the
BAMO Tetramer through Least-Squares Refinement
of the Model

Type	Distances(Å)	Averages	Type	Angles(°)	Averages
C-O	1.411(7)	1.416	C-O-C	112.1(5)	112.9
	1.419(6)			113.7(5)	
	1.420(7)		O-C-C	108.5(5)	109.1
	1.413(7)			108.5(5)	
1.520(8)	109.3(5)	C-C-C		110.0(5)	
1.526(8)	109.7(5)				
1.519(8)	107.2(6)				
1.532(7)	111.5(6)				
1.509(8)	110.9(5)				
1.535(8)	105.9(6)				
1.528(8)	110.4(4)				
1.531(7)	110.0(3)				
C-N	1.459(9)	1.460	N-C-C	111.7(5)	109.0
	1.440(9)			110.4(6)	
	1.472(10)			105.9(6)	
	1.468(8)			110.8(7)	
N=N	1.254(23)	1.170	N-N-C	108.9(5)	115.7
	1.130(25)			114.4(7)	
	1.175(12)			114.7(9)	
	1.163(7)			116.6(10)	
N≡N	1.159(22)	1.143	N-N-N	117.1(6)	171.5
	1.240(25)			173.3(10)	
	1.120(12)			172.7(12)	
	1.141(8)			169.1(14)	
				170.8(9)	

* The figures in parentheses are the estimated standard deviations in the final digits of each value. Particularly large esd's are noted with asterisks, and are due to azido disorder. Averages are weighted averages (with the weights equal to the reciprocal square of the esd's).

IV. The Crystal and Molecular Structure of the Energetic Polymer, $(\text{BAMO})_n$

Polymers of BAMO show a tendency to crystallize even without special treatment such as annealing or stretching. The initial samples of $(\text{BAMO})_n$ investigated were rubbery cross-linked polymers which contained, besides BAMO, small concentrations of cross-linking agents (diols). These samples could not be softened and stretched by solvents or heating, and thus did not yield fibrous diffraction patterns which could provide unit cell and molecular structure information. However, they did display a limited number of powder rings in their x-ray diffraction patterns, which was an encouraging indication that micro-domains of crystalline ordering existed even in the elastic cross-linked form of the polymer.

Samples of linear $(\text{BAMO})_n$ polymers of M.W. 20,000 were later made available which were produced without the addition of cross-linking agents. Initial treatment of these samples centered on a search for a method for softening (or dissolving) these polymers in a solvent, with the aim of either stretching, re-depositing, or extruding the softened polymer in a more ordered crystalline form. Although these attempts did not succeed in their aim, the presence of a cyclic tetramer side-product was discovered, and led to the characterization of the molecular structure of the tetramer, which is a close analog to the actual polymer.

A breakthrough in the analysis of the linear polymer occurred when it was discovered that $(\text{BAMO})_n$ could be quickly melted and stretched by immersion in hot (ca $90^\circ\text{C}.$) water without any sign of decomposition. (Slower heating in air, or more extended heating did lead to slight darkening of the substance and no improvement in molecular orientation). X-ray diffraction films of this stretched sample display a characteristic x-ray fiber pattern (see Fig. 5). This pattern consists of ca. 20 extended, but distinct, spots which are much stronger, relative to background, than the powder rings observed with unstretched $(\text{BAMO})_n$.

From layer lines and spots along the stretch direction of the polymer, it is possible to immediately determine the fiber repeat distance of the polymer; i.e., the distance between exact repeats of the polymer units along the chain direction. This was found to be $4.75 \text{ \AA}$; this short repeat unit is only consistent with a non-helical planar zig-zag conformation in the $(\text{BAMO})_n$ backbone.

Spots along the equator (the line perpendicular to the stretch direction) reveal the other dimensions of the crystalline unit cell, which correspond to chain-chain packing approaches. However, this information can only be obtained from a fiber pattern by indexing a few of the equatorial spots in a self-consistent manner, using the indices and the accurate locations of the peaks to calculate a set of cell dimensions, and then checking that this cell

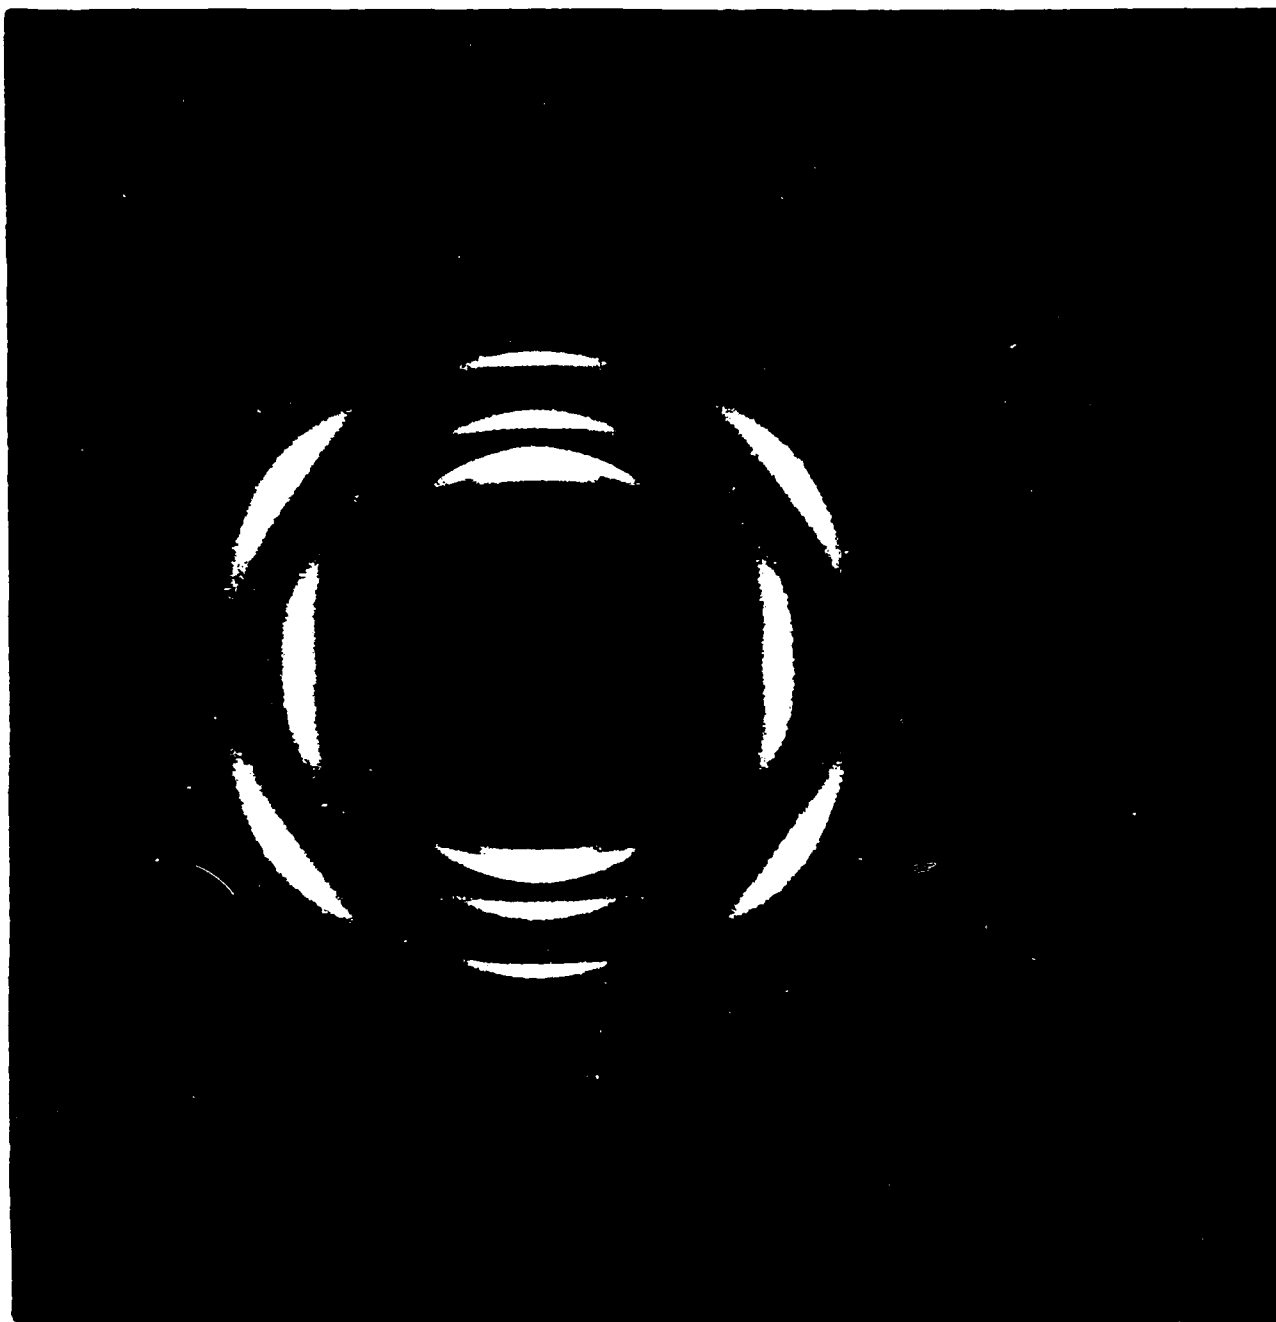


Fig. (5) The fiber x-ray diffraction pattern from stretched polymers of BAMO. The stretch direction is horizontal in this illustration. The many small spots in this photograph are diffraction spots from small crystals of the BAMO tetramer (an impurity in this polymer sample).

correctly predicts the location of all the other spots. A computer program was written to go through such trials in a systematic way. Over 20,000 indexing trials were quickly evaluated, and one orthorhombic cell fit the pattern better than all others. The cell thus determined for $(\text{BAMO})_n$ was $a = 5.77$, $b = 15.01$, and $c = 4.75 \text{ \AA}$. The calculated density from this cell is 1.356 g/cm^3 , which compares well with the tetramer density (1.336 g/cm^3), and a measured density of 1.30 g/cm^3 (from the report of Miller et al., 1981; probably refers to a cross-linked polymer sample).

All of the many components necessary for building a reasonable full crystal structure for $(\text{BAMO})_n$ have now been determined by our preliminary studies and may be systematically assembled by our computer modelling programs. The various types of information used are listed below.

1. Methylazido distances and angles - from BAMO monomer electron diffraction study
2. Backbone distances and angles - from BAMO tetramer x-ray study
3. Backbone torsions - fixed near 180° by short fiber repeat distance
4. Side-chain torsions - many possible starting values examined and ranked by non-bonded energy calculations ("Molecular Mechanics" Programs)
5. Packing - many aspects of packing are approximately fixed by size of cell and shape of chain; extinction along $0k0$ (strongly suggested by pattern) required half-cell translational operation along y

Two criteria are being used to recognize the true crystal structure; the R-factor ($R = \Sigma |F_o - F_c| / \Sigma F_o$), which expresses the average disagreement between the observed spot intensities and the model's calculated spot intensities, and the non-bonded contact energy, which rises rapidly if adjacent molecules make contacts which are less than accepted van der Waals contact distances.

A number of fully ordered crystal structure models have been assembled, tested, and refined with the LALS (linked-atom least squares) program. Two promising models are depicted in Figs. 6 and 7. Packing model I gives a low R-factor of 18%, but it contains some short azido-azido contacts of 2.5-2.6 Å, which are too small. (The tetramer crystal had none less than 3.1 Å). Packing model II has better contacts (N...N minimum 2.9 Å), but gives a higher R-factor (ca. 35%). A better fit to both criteria is anticipated with the aid of an interactive computer graphics system which is now available. At this point, many features of the polymer's structure are emerging.

The cell geometry requires the same zig-zag backbone for the chain in all models. This planar backbone always lies in or near the AC plane. Another layer of chain backbones lies at $Y = 1/2$, giving the oko extinction observed in the data. The methylazido chains extend into and fill in the interlayer space. Detailed models differ only in the conformation of these side-chains, and the relative translation of the AC layers.

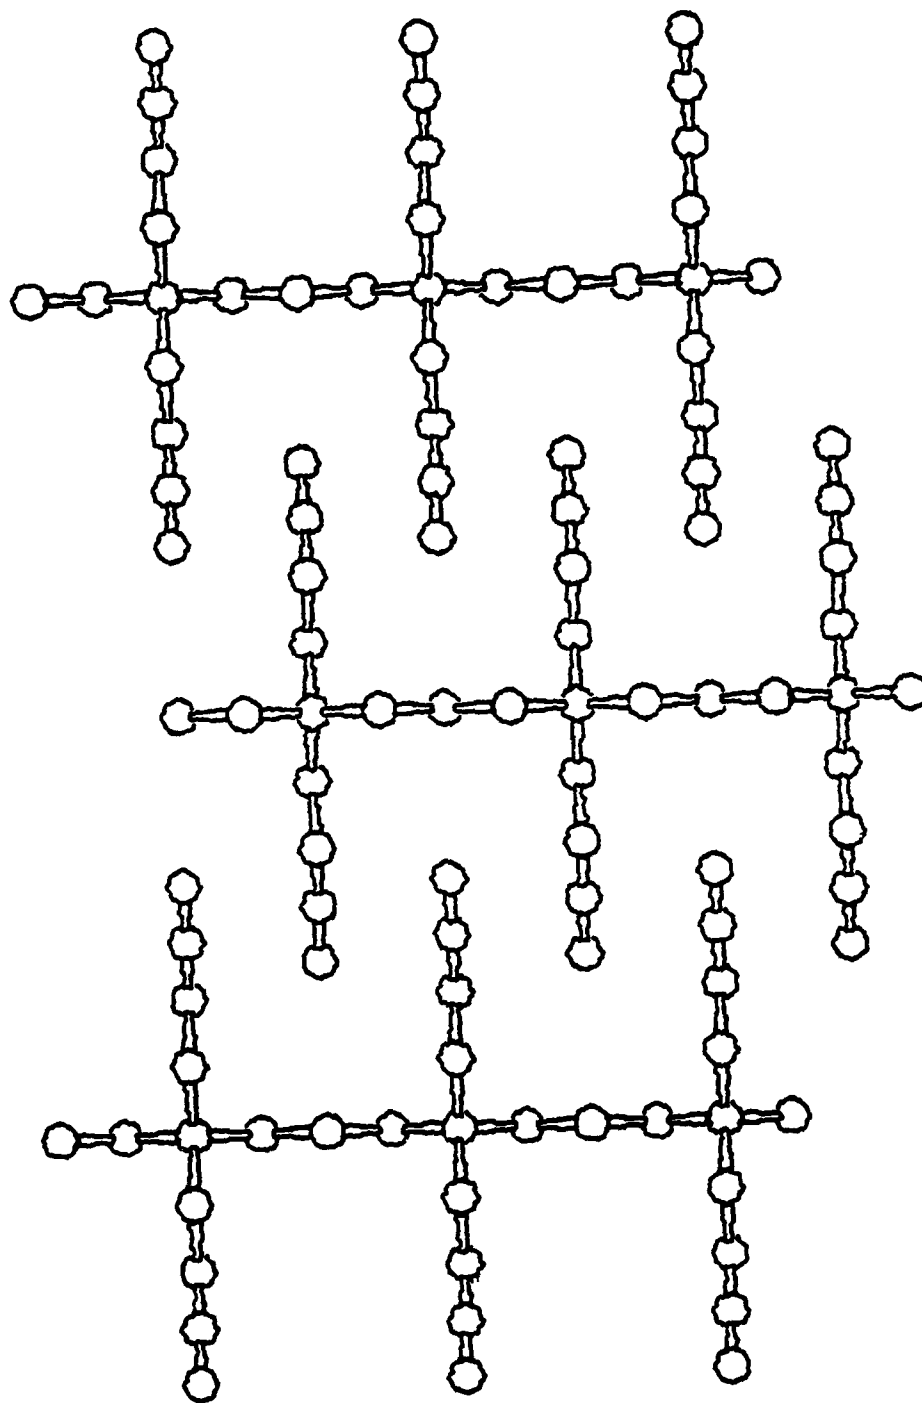


Fig. (6) Packing model I for $(\text{BAMO})_n$.


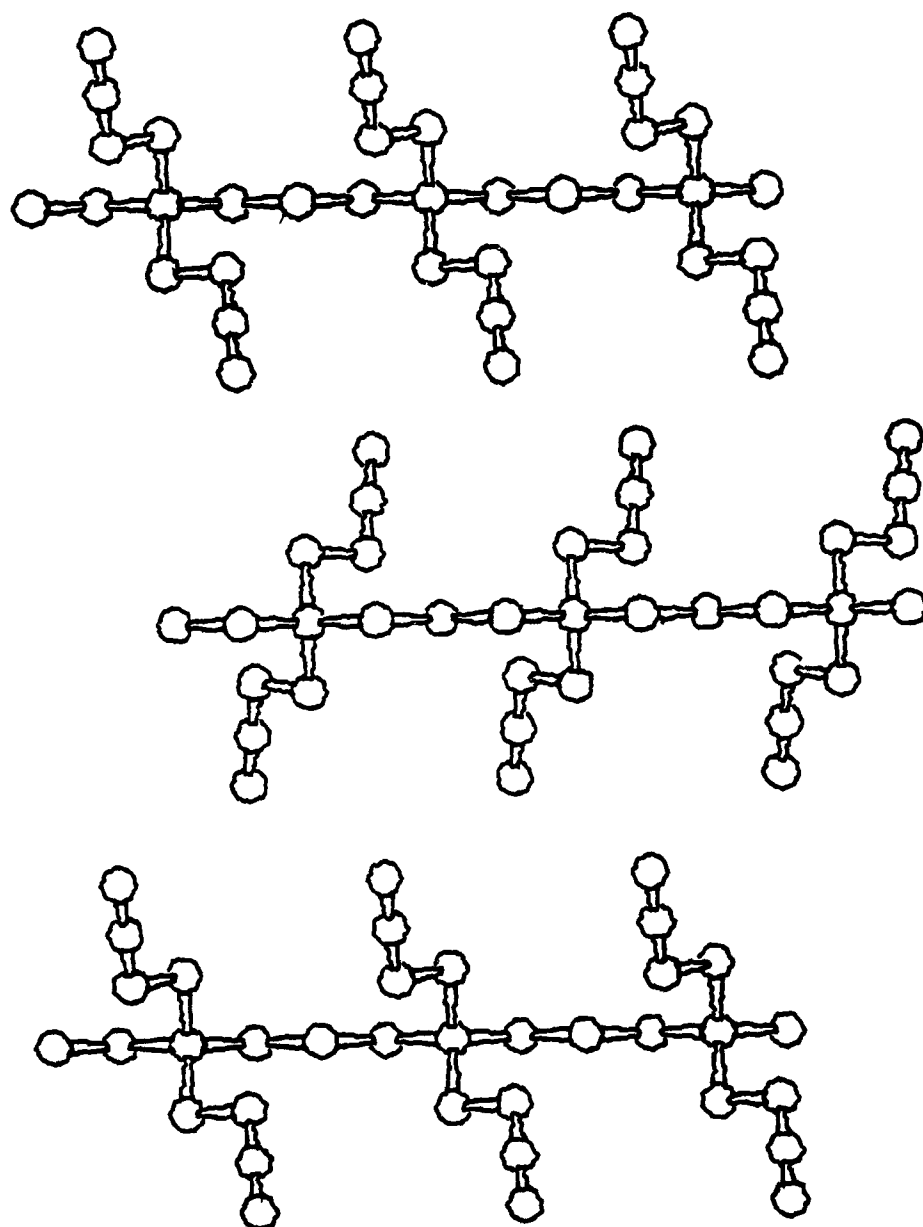



Fig. (7) Packing model II for (BAMO)_n.

V. The Crystal Structure of a Tetranitrodifluoro Monomer:
4,7-bis(Dinitrofluoromethyl)-1,3-dioxepane

A possible route for the synthesis of dense energetic polymers suggested by Dr. Horst Adolph (Naval Surface Weapons Center, White Oak) involves the preparation, and subsequent ring-opening polymerization of cyclic formals:

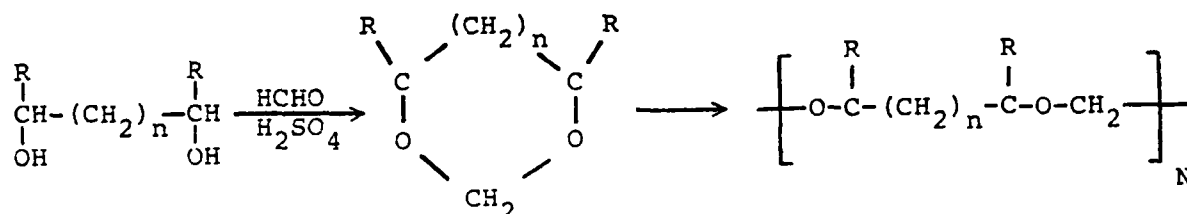

R is chosen to be an energetic substituent. Dr. Adolph provided crystals of one such monomer for structural analysis, a tetranitrodifluoro compound:

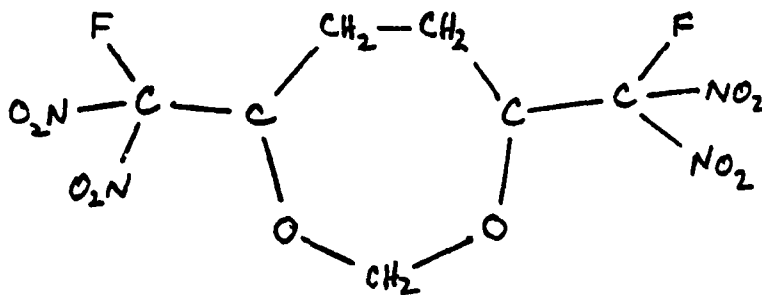

This compound is quite stable despite its high degree of nitro-substitution, and forms clear colorless crystals. The unit cell parameters are $a = 14.306(2)$, $b = 11.364(2)$, $c = 10.854(2)$ Å, $\beta = 128.93(2)^\circ$ and the crystal space group symmetry is $C2/c$. The crystal density calculated from this cell is 1.675 g/cm^3 .

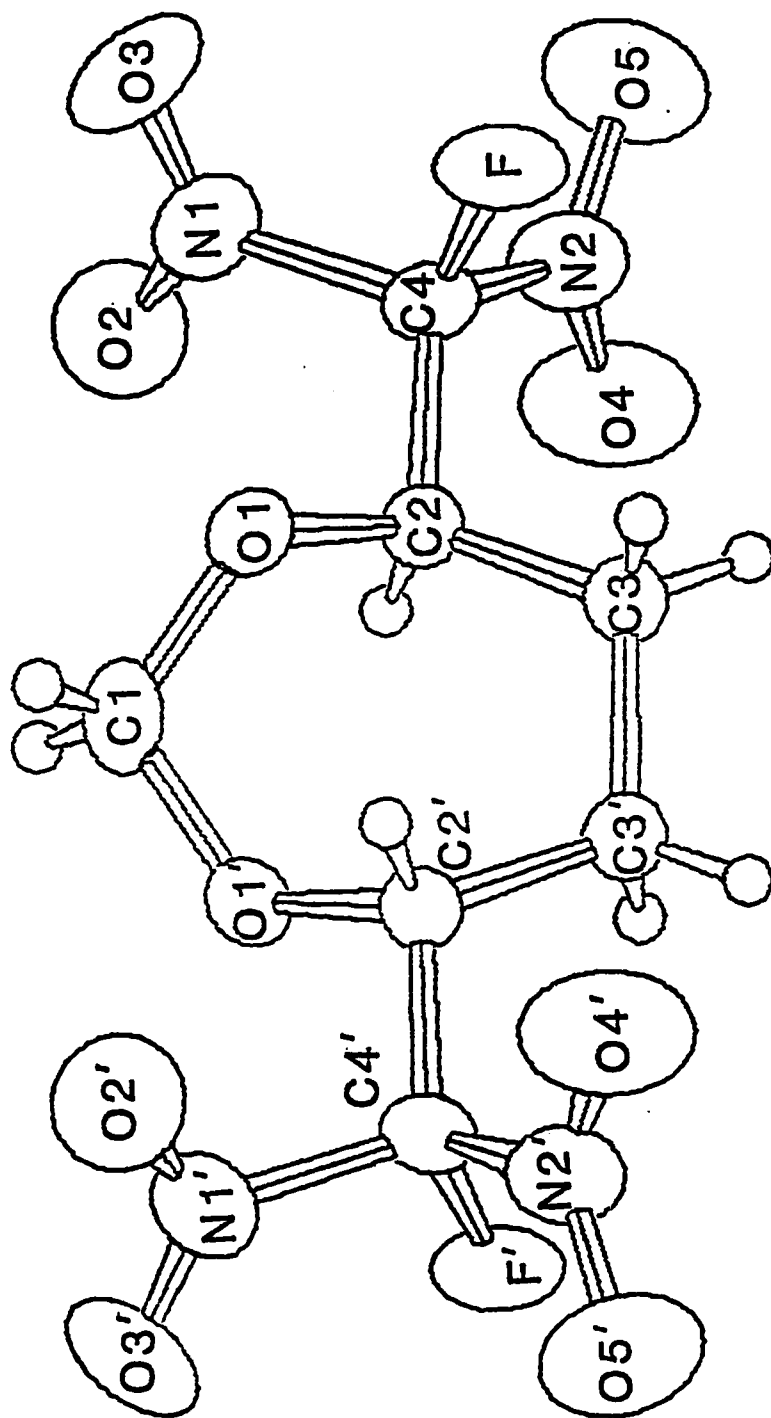


Fig. (8) The molecular structure of 4,7-bis(dinitrofluoromethyl)-1,3-dioxepane. This computer-generated perspective view is an exact representation of the refined atomic coordinates of the molecule from the diffraction analysis.

Table 3. Bond Distances, Angles, and Selected Torsions
for 4,7-bis(Dinitrofluoromethyl)-1,3-dioxepane


Distances (Å.)		Angles (°)	
C(1)-O(1)	1.405(4)	O(1)-C(1)-O(1)'	111.9(5)
O(1)-C(2)	1.430(5)	C(1)-O(1)-C(2)	114.3(3)
C(2)-C(3)	1.522(6)	O(1)-C(2)-C(4)	104.3(3)
C(3)-C(3)'	1.531(10)	O(1)-C(2)-C(3)	108.8(3)
C(2)-C(4)	1.495(7)	C(4)-C(2)-C(3)	113.1(4)
C(4)-F	1.333(5)	C(2)-C(4)-F	113.9(4)
C(4)-N(1)	1.530(6)	C(2)-C(4)-N(1)	109.5(4)
N(1)-O(2)	1.181(5)	C(2)-C(4)-N(2)	115.1(4)
N(1)-O(3)	1.228(6)	F -C(4)-N(1)	106.8(4)
C(4)-N(2)	1.517(6)	F -C(4)-N(2)	105.7(4)
N(2)-O(4)	1.153(5)	N(1)-C(4)-N(2)	105.2(3)
N(2)-O(5)	1.201(6)	C(2)-C(3)-C(3)'	112.8(3)
Torsions(°)		C(4)-N(1)-O(2)	115.6(5)
		C(4)-N(1)-O(3)	116.0(5)
O(1)'-C(1)-O(1)-C(2)	45.9(2)	O(2)-N(1)-O(3)	128.3(5)
C(1)-O(1)-C(2)-C(3)	-97.6(4)	C(4)-N(2)-O(4)	118.1(5)
O(1)-C(2)-C(3)-C(3)'	70.7(6)	C(4)-N(2)-O(5)	116.0(5)
C(2)-C(3)-C(3)'-C(2)'	-49.8(8)	O(4)-N(2)-O(5)	125.8(6)
O(1)-C(2)-C(4)-F	70.6(4)		
F -C(4)-N(1)-O(3)	-3.5(6)		
F -C(4)-N(2)-O(5)	-33.9(6)		

The crystal and molecular structures were obtained by routine application of the symbolic addition procedure (Karle and Karle, 1966). Bond distances and angles for this molecule are listed in Table 3, and a graphic representation of the molecule is illustrated in Fig. 8. This structure appears to be the first ever reported of a compound containing a dinitro-carbon atom. Only two prior reports have so far been found dealing with mono-nitro substitution on tetrahedral carbon atoms.


The results of this study were transmitted to Dr. Adolph and also to Dr. Joyce Kaufman (Johns Hopkins Univ.) for quantum chemical analysis of the electrostatic potential and reactivity of this monomer. A short article is being prepared for publication in *Acta Crystallographica*.

VI. The Crystal Structure of a Diaminodioxadiazole, a Synthetic Intermediate Originating in Research on the Synthesis of New High Explosives

The compound bis(5-nitro-1,2,4-oxadiazole),



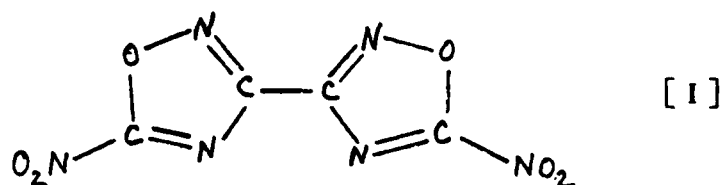


has been proposed as a possibly useful high density explosive (C. Coon, 1981). However, synthesis by direct nitration of the unsubstituted dioxadiazole did not proceed, even under harsh conditions. An alternative synthetic route would be via the synthetic intermediate II, a diaminodioxadiazole:

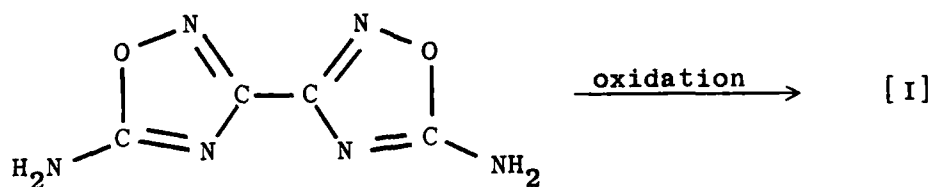

Compound II was synthesized by Dr. Coon, but the above reaction also did not proceed, even with very strong oxidizers. An x-ray diffraction study of II was proposed to establish the

nature of the bonding in the starting material. A number of structures might be possible which differ only in the placement of the hydrogen atoms:

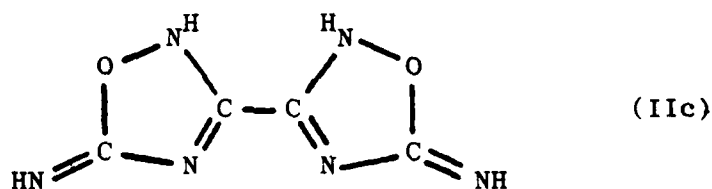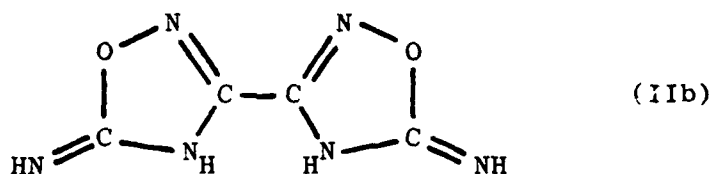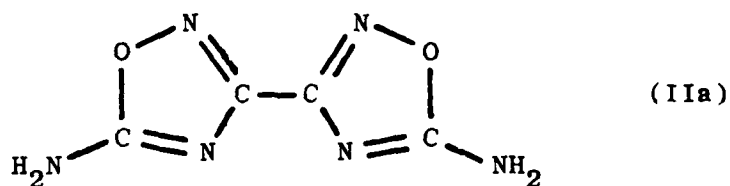

A sample of II was obtained from Dr. Coon and analyzed by means of x-ray single-crystal diffraction. The results unambiguously locate the hydrogen atoms, and corroborate that the structure is IIa. We are informed that this is also consistent with a ^{13}C -NMR spectral study. Bond distances and angles of II are displayed in Fig. 9. The extraordinary stability of this compound may be reflected in the detailed geometry of the amino group. The entire molecule, including the amino hydrogen atoms, is planar. This fact, coupled

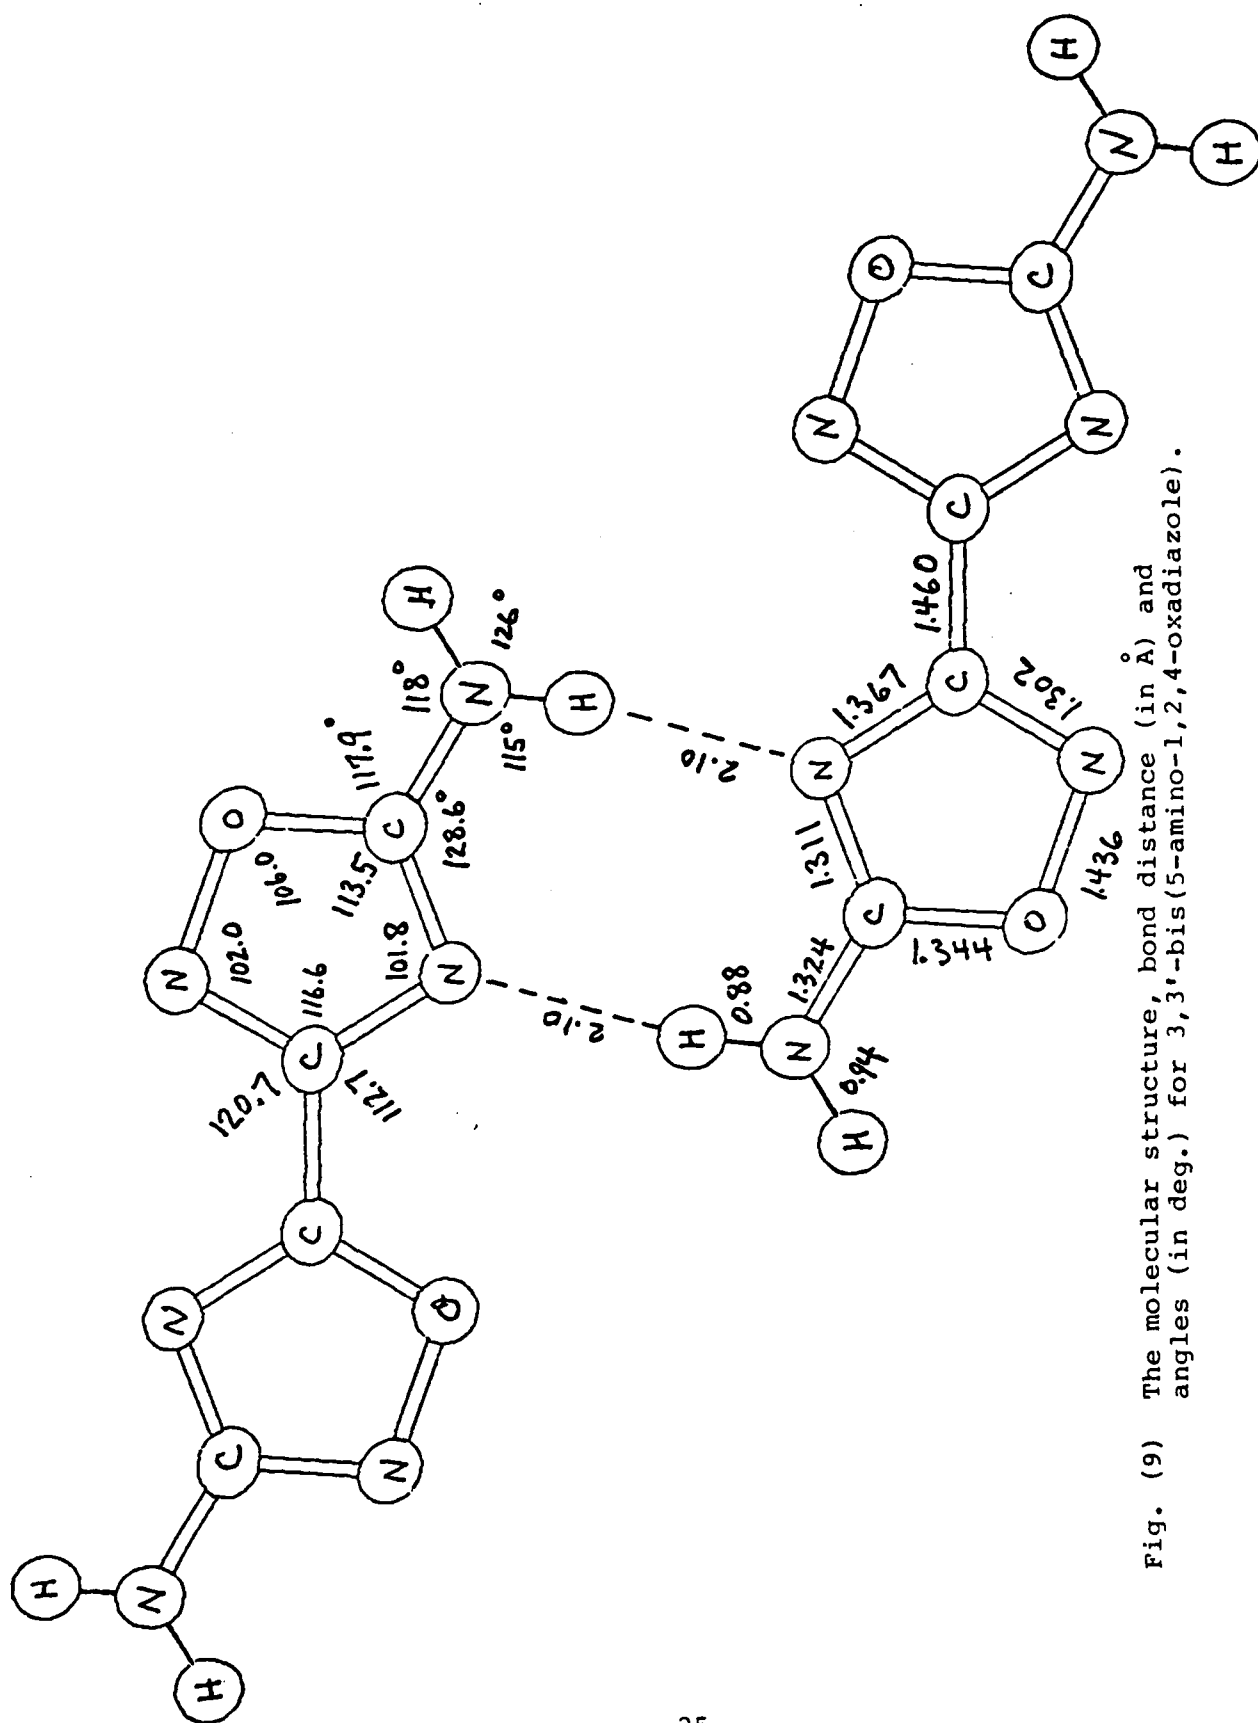


Fig. (9) The molecular structure, bond distance (in Å) and angles (in deg.) for 3,3'-bis(5-amino-1,2,4-oxadiazole).

with the very short length (1.324 Å) of the CN "single" bond, indicates extensive conjugation between the ring electrons and the amino lone-pair electrons. Thus, this amine bears little resemblance to a primary aliphatic amine. Structurally, it is related to the aromatic amines or to the amino portion of an amide group. Another class of compounds which contain similar conjugated exocyclic amino groups are the pyrimidines. This information was transmitted to Dr. Coon, in hopes that it might aid in guiding future efforts towards the synthesis of I.

VI. References

1. Coon, C. F., (1981), private communication.
2. Karle, J. and Karle, I. L. (1966), Acta Crystallogr. 21, 849.
3. Miller, R. S., Miller, P. A., Hall, T. N., and Reed, R. (1981) Naval Research Rev. 33, 21-36.

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. L.V. Schmidt Assistant Secretary of the Navy (R,E, and S) Room 5E 731 Pentagon Washington, D.C. 20350	1	Dr. F. Roberto Code AFRPL MKPA Edwards AFB, CA 93523	1
Dr. A.L. Slafkosky Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1	Dr. L.H. Caveny Air Force Office of Scientific Research Directorate of Aerospace Sciences Bolling Air Force Base Washington, D.C. 20332	1
Dr. Richard S. Miller Office of Naval Research Code 413 Arlington, VA 22217	10	Mr. Donald L. Ball Air Force Office of Scientific Research Directorate of Chemical Sciences Bolling Air Force Base Washington, D.C. 20332	1
Mr. David Siegel Office of Naval Research Code 260 Arlington, VA 22217	1	Dr. John S. Wilkes, Jr. FJSRL/NC USAF Academy, CO 80840	1
Dr. R.J. Marcus Office of Naval Research Western Office 1030 East Green Street Pasadena, CA 91106	1	Dr. R.L. Lou Aerojet Strategic Propulsion Co. P.O. Box 15699C Sacramento, CA 95813	1
Dr. Larry Peebles Office of Naval Research East Central Regional Office 666 Summer Street, Bldg. 114-D Boston, MA 02210	1	Dr. V.J. Keenan Anal-Syn Lab Inc. P.O. Box 547 Paoli, PA 19301	1
Dr. Phillip A. Miller Office of Naval Research San Francisco Area Office One Hallidie Plaza, Suite 601 San Francisco, CA 94102	1	Dr. Philip Howe Army Ballistic Research Labs ARRADCOM Code DRDAR-BLT Aberdeen Proving Ground, MD 21005	1
Mr. Otto K. Heiney AFATL - DLDL Elgin AFB, FL 32542	1	Mr. L.A. Watermeier Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1
Mr. R. Geisler ATTN: MKP/MS24 AFRPL Edwards AFB, CA 93523	1	Dr. W.W. Wharton Attn: DRSMI-RKL Commander U.S. Army Missile Command Redstone Arsenal, AL 35898	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. R.G. Rhoades Commander Army Missile Command DRSMI-R Redstone Arsenal, AL 35898	1	Dr. E.H. Debutts Hercules Inc. Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. W.D. Stephens Atlantic Research Corp. Pine Ridge Plant 7511 Wellington Rd. Gainesville, VA 22065	1	Dr. James H. Thacher Hercules Inc. Magna Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. A.W. Barrows Ballistic Research Laboratory USA ARRADCOM DRDAR-BLP Aberdeen Proving Ground, MD 21005	1	Mr. Theodore M. Gilliland Johns Hopkins University APL Chemical Propulsion Info. Agency Johns Hopkins Road Laurel, MD 20810	1
Dr. C.M. Frey Chemical Systems Division P.O. Box 358 Sunnyvale, CA 94086	1	Dr. R. McGuire Lawrence Livermore Laboratory University of California Code L-324 Livermore, CA 94550	1
Professor F. Rodriguez Cornell University School of Chemical Engineering Olin Hall, Ithaca, N.Y. 14853	1	Dr. Jack Linsk Lockheed Missiles & Space Co. P.O. Box 504 Code Org. 83-10, Bldg. 154 Sunnyvale, CA 94088	1
Defense Technical Information Center DTIC-DDA-2 Cameron Station Alexandria, VA 22314	12	Dr. B.G. Craig Los Alamos National Lab P.O. Box 1663 NSP/DOD, MS-245 Los Alamos, NM 87545	1
Dr. Rocco C. Musso Hercules Aerospace Division Hercules Incorporated Allegheny Ballistic Lab P.O. Box 210 Washington, D.C. 21502	1	Dr. R.L. Rabie WX-2, MS-952 Los Alamos National Lab. P.O. Box 1663 Los Alamos NM 37545	1
Dr. Ronald L. Simmons Hercules Inc. Eglin AFATL/DLGL Eglin AFB, FL 32542	1	Dr. B. Rogers, WX-2 Los Alamos Scientific Lab. P.O. Box 1663 Los Alamos, NM 87545	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. R. Brown Naval Air Systems Command Code 330 Washington, D.C. 20361	1	Dr. J. Schnur Naval Research Lab. Code 6510 Washington, D.C. 20375	1
Dr. H. Rosenwasser Naval Air Systems Command AIR-310C Washington, D.C. 20360	1	Mr. R. Beauregard Naval Sea Systems Command SEA 64E Washington, D.C. 20362	1
Mr. B. Sobers Naval Air Systems Command Code 03P25 Washington, D.C. 20360	1	Mr. G. Edwards Naval Sea Systems Command Code 62R3 Washington, D.C. 20362	1
Dr. L.R. Rothstein Assistant Director Naval Explosives Dev. Engineering Dept. Naval Weapons Station Yorktown, VA 23691	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, PA 19112	1
Dr. Lionel Dickinson Naval Explosive Ordnance Disposal Tech. Center Code D Indian Head, MD 20640	1	Dr. H.G. Adolph Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1
Mr. C.L. Adams Naval Ordnance Station Code PM4 Indian Head, MD 20640	1	Dr. T.D. Austin Naval Surface Weapons Center Code R16 Indian Head, MD 20640	1
Mr. S. Mitchell Naval Ordnance Station Code 5253 Indian Head, MD 20640	1	Dr. T. Hall Code R-11 Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910	1
Dr. William Tolles Dean of Research Naval Postgraduate School Monterey, CA 93940	1	Mr. G.L. Mackenzie Naval Surface Weapons Center Code R101 Indian Head, MD 20640	1
Naval Research Lab. Code 6100 Washington, D.C. 20375	1	Dr. K.F. Mueller Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. J. Murrin Naval Sea Systems Command Code 62R2 Washington, D.C. 20362	1	Dr. A. Nielsen Naval Weapons Center Code 385 China Lake, CA 93555	1
Dr. D.J. Pastine Naval Surface Weapons Center Code R04 White Oak Silver Spring, MD 20910	1	Dr. R. Reed, Jr. Naval Weapons Center Code 388 China Lake, CA 93555	1
Mr. L. Roslund Naval Surface Weapons Center Code R122 White Oak, Silver Spring MD 20910	1	Dr. L. Smith Naval Weapons Center Code 3205 China Lake, CA 93555	1
Mr. M. Stosz Naval Surface Weapons Center Code R121 White Oak Silver Spring, MD 20910	1	Dr. B. Douda Naval Weapons Support Center Code 5042 Crane, Indiana 47522	1
Dr. E. Zimmet Naval Surface Weapons Center Code R13 White Oak Silver Spring, MD 20910	1	Dr. A. Faulstich Chief of Naval Technology MAT Code 0716 Washington, D.C. 20360	1
Dr. D. R. Derr Naval Weapons Center Code 388 China Lake, CA 93555	1	LCDR J. Walker Chief of Naval Material Office of Naval Technology MAT, Code 0712 Washington, D.C. 20360	1
Mr. Lee N. Gilbert Naval Weapons Center Code 3205 China Lake, CA 93555	1	Mr. Joe McCartney Naval Ocean Systems Center San Diego, CA 92152	1
Dr. E. Martin Naval Weapons Center Code 3858 China Lake, CA 93555	1	Dr. S. Yamamoto Marine Sciences Division Naval Ocean Systems Center San Diego, CA 91232	1
Mr. R. McCarten Naval Weapons Center Code 3272 China Lake, CA 93555	1	Dr. G. Bosmajian Applied Chemistry Division Naval Ship Research & Development Center Annapolis, MD 21401	1
		Dr. H. Shuey Rohn and Haas Company Huntsville, Alabama 35801	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. J.F. Kincaid Strategic Systems Project Office Department of the Navy Room 301 Washington, D.C. 20376	1	Dr. C.W. Vriesen Thiokol Elkton Division P.O. Box 241 Elkton, MD 21921	1
Strategic Systems Project Office Propulsion Unit Code SP2731 Department of the Navy Washington, D.C. 20376	1	Dr. J.C. Hinshaw Thiokol Wasatch Division P.O. Box 524 Brigham City, Utah 84302	1
Mr. E.L. Throckmorton Strategic Systems Project Office Department of the Navy Room 104B Washington, D.C. 20376	1	U.S. Army Research Office Chemical & Biological Sciences Division P.O. Box 12211 Research Triangle Park NC 27709	1
Dr. D.A. Flanigan Thiokol Huntsville Division Huntsville, Alabama 35807	1	Dr. R.F. Walker USA ARADCOM DRDAR-LCE Dover, NJ 07801	1
Mr. G.F. Mangum Thiokol Corporation Huntsville Division Huntsville, Alabama 35807	1	Dr. T. Sinden Munitions Directorate Propellants and Explosives Defence Equipment Staff British Embassy 3100 Massachusetts Ave. Washington, D.C. 20008	1
Mr. E.S. Sutton Thiokol Corporation Elkton Division P.O. Box 241 Elkton, MD 21921	1	Capt. S. Shackelford AFRPL/LKLR Edwards AFB, CA 93523	1
Dr. G. Thompson Thiokol Wasatch Division MS 240 P.O. Box 524 Brigham City, UT 84302	1	Dr. Merrill K. King Atlantic Research Corp. 5390 Cherokee Avenue Alexandria, VA 22314	1
Dr. T.F. Davidson Technical Director Thiokol Corporation Government Systems Group P.O. Box 9253 Ogden, Utah 84403	1	Dr. W. Wharton Army Missile Command DRSMI-RK Redstone Arsenal, AL 35898	1
		Dr. David C. Sayles Ballistic Missile Defense Advanced Technology Center P.O. Box 1500 Huntsville, AL 35807	1

DISTRIBUTION LIST

<u>No. Copies</u>		<u>No. Copies</u>
1	Dr. Kurt Baum Fluorochem, Inc. 680 South Ayon Ave. Azusa, CA 91702	1 Dr. R. Atkins Naval Weapons Center Code 3852 China Lake, CA 93555
1	Professor J. H. Boyer Univ. of Illinois Dept. of Chemistry Box 4348 Chicago, Illinois 60680	1 Dr. May L. Chan Naval Weapons Center Code 3244 China Lake, CA 93555
1	Dr. Joyce J. Kaufman The Johns Hopkins University Department of Chemistry Baltimore, MD 21218	1 Dr. T. B. Joyner Naval Weapons Center Code 3264 China Lake, CA 93555
1	Dr. C. Coon Lawrence Livermore Lab. University of California P.O. Box 808 Livermore, CA 94550	1 Dr. R. A. Rhein Naval Weapons Center Code 3244 China Lake, CA 93555
1	Professor J. C. Chien University of Massachusetts Department of Chemistry Amherst, MA 03003	1 Dr. B. David Halpern Polysciences, Inc. Paul Valley Industrial Park Warrington, PA 18976
1	Professor P. Lillya University of Massachusetts Department of Chemistry Amherst, MA 03003	1 Dr. Karl O. Christe Rockwell International 6633 Canoga Avenue Canoga Park, CA 91304
1	Prof. Richard A. Reinhardt Naval Postgraduate School Physics & Chemistry Department Monterey, CA 93940	1 Dr. M. B. Frankel Rockwell International Rocketdyne Division 6633 Canoga Avenue Canoga Park, CA 91304
1	Dr. J. Karle Naval Research Laboratory Code 6030 Washington, D.C. 20375	1 Dr. D. L. Ross SRI International 333 Ravenswood Avenue Menlo Park, CA 94025
1	Dr. M. J. Kamlet Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910	1 Mr. Ed van Ribbink Space Ordnance Systems 25977 San Canyon Road Canyon Country, CA 91351

SYN

6/81

DISTRIBUTION LIST

	<u>No. Copies</u>	<u>No. Copies</u>
Mr. M. Baron SP 27314 Strategic Systems Project Office Department of the Navy Washington, D.C. 20376	1	
Dr. J. Hinshaw Thiokol/Wasatch Div. P.O. Box 524 Brigham City, Utah 84302	1	