

AD-A280 995



1

OFFICE OF NAVAL RESEARCH

CONTRACT N00014-94-1-0101

R&T Code 31321075

Technical Report No. 7

NEW INITIATORS FOR CONTROLLED RADICAL POLYMERIZATION  
OF ACRYLIC MONOMERS

by

Daniela Mardare, Krzysztof Matyjaszewski

Published

in the

ACS Polym. Preprints, in press

Carnegie Mellon University  
Department of Chemistry  
4400 Fifth Avenue  
Pittsburgh, PA 15213

June 30, 1994

Reproduction in whole or in part is permitted for any purpose of the United States Government

This document has been approved for public release and sale;  
its distribution is unlimited.

94-20034



94 6 29 100

**Best  
Available  
Copy**

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE June 30, 1994		3. REPORT TYPE AND DATES COVERED Technical Report # 7	
4. TITLE AND SUBTITLE New Initiators for Controlled Radical Polymerization of Acrylic Monomers				5. FUNDING NUMBERS N00014-94-1-0101	
6. AUTHOR(S) Daniela Mardare, Krzysztof Matyjaszewski					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Carnegie Mellon University Department of Chemistry 4400 Fifth Avenue Pittsburgh, PA 15213				8. PERFORMING ORGANIZATION REPORT NUMBER N00014-94-1-0101	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Department of the Navy Office of Naval Research 800 North Quincy Street Arlington, VA 22217-5000				10. SPONSORING/MONITORING AGENCY REPORT NUMBER Technical Report # 7	
11. SUPPLEMENTARY NOTES ACS Polym. Preprints, in press					
12a. DISTRIBUTION/AVAILABILITY STATEMENT				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words)  Polymerization of acrylic monomers was redox initiated by mixtures (1:1) of transition metal derivatives (acetates, metallocenes) with arenediazonium salts. In most cases, molecular weights increase with the conversion and polydispersities are lower than in a typical radical or anionic polymerization at these temperatures. Trapping experiments and relative monomer reactivities based on copolymerization studies indicate that these polymerizations proceed via a radical mechanism. The improved polymerization control can be ascribed to an equilibrium between growing radicals and dormant persistent radicals.					
14. SUBJECT TERMS				15. NUMBER OF PAGES	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Classified	18. SECURITY CLASSIFICATION OF THIS PAGE Classified	19. SECURITY CLASSIFICATION OF ABSTRACT Classified		20. LIMITATION OF ABSTRACT UL	

# NEW INITIATORS FOR CONTROLLED RADICAL POLYMERIZATION OF ACRYLIC MONOMERS

Daniela Mardare and Krzysztof Matyjaszewski\*  
Department of Chemistry  
Carnegie Mellon University  
4400 Fifth Avenue  
Pittsburgh PA, 15213

## Introduction

The successful design of new well defined polymers and copolymers requires the enhanced control over the structure, reactivity and chemoselectivity of the propagating species. This usually happens in living systems in which transfer and termination are below detection level. However, in some systems transfer and termination cannot be completely avoided. Nevertheless, it is possible to convert nonliving anionic, cationic and free radical polymerizations into controlled polymerizations yielding well defined polymers and copolymers. One approach is based on the modification of the reactive chain ends with transition metal complexes. It is possible to tune the electronic and stereochemical properties of the complexes by adjustment of Lewis acidity and the oxidation state of the metal as well as the ligand sphere. Thus, the reactivity of the modified propagating chain-ends can be adjusted over a wide range, allowing the polymerization to proceed under well controlled conditions.

The enhanced control was observed in radical polymerization of vinyl acetate in the presence of transition metal derivatives such as chromium acetate ("aged" benzoyl peroxide/Cr(OAc)<sub>2</sub>)<sup>1</sup> or chromium acetate and/or chromium alkyls coordinated by macrocyclic amine.<sup>2</sup> Additionally, controlled polymerization of electron-accepting monomers (methyl methacrylate, di-2-ethylhexyl itaconate) was achieved using lanthanum versate/diazonium salts.<sup>3</sup>


In this paper, we report the controlled radical polymerization of acrylic monomers (methyl acrylate, methyl methacrylate), using as initiating systems combinations of transition metal derivatives with arenediazonium salts (components of Sandmeyer reaction).

## Experimental

Transition metal derivatives (chromium (III) acetate, rhodium (II) acetate, cobalt (II) acetate, cerium (III) acetate, dicyclopentadienylchromium, Cp<sub>2</sub>Cr, dicyclopentadienylzirconium dichloride, Cp<sub>2</sub>ZrCl<sub>2</sub>, dicyclopentadienylruthenium, Cp<sub>2</sub>Ru) were used without any purification, as received from Aldrich. p-Chlorobenzenediazonium tetrafluoroborate (DS) was prepared by diazotization of p-chloroaniline hydrochloride with sodium nitrite in aqueous acid media, at 0°C, for 15 minutes. Then, sodium tetrafluoroborate was added and the reaction mixture stirred for additional 45 minutes, at 0°C. Inhibitors were removed from acrylic monomers by washing with a 5% NaOH aqueous solution, followed by drying over MgSO<sub>4</sub> and distilling over CaH<sub>2</sub>. Tetrahydrofuran was freshly distilled over Na-anthracene. Polymerizations were carried out in degassed and sealed tubes under Ar, in a mixed solvent THF-acetone, at 40°C. Polymers were precipitated in hexane, filtered, dried and characterized by GPC and <sup>1</sup>H-NMR. Molecular weights and molecular weight distributions were determined by gel permeation chromatography (GPC), using a Waters 510 pump equipped with a 410 differential refractometer and UV detector, using THF as eluent with a flow rate of 1.0 mL·min<sup>-1</sup>, and with three ULTRASTYRAGEL columns (100Å, 500 Å and Linear) in series. The molecular weight calibration curve was obtained using polystyrene standards. PMMA microstructures were determined by <sup>1</sup>H-NMR, spectra being recorded with a Nicolet 300 MHz spectrometer in CDCl<sub>3</sub> solutions, at 25°C.

## Results and Discussion

According to literature<sup>4,5</sup>, some organometallic compounds can be oxidized in the presence of arenediazonium salts, which are reduced to phenyl-based radicals (eq. 1).



Mt = Rh<sup>II</sup>, Cr<sup>II</sup>, Co<sup>II</sup>, Ce<sup>III</sup>, Ru<sup>II</sup>, Zr<sup>IV</sup>  
R = OAc, cyclopentadienyl

Figures 1-3 show typical behavior of polymerization of methyl methacrylate (MMA) initiated by mixtures of transition metal acetates with p-chlorobenzenediazonium tetrafluoroborate.

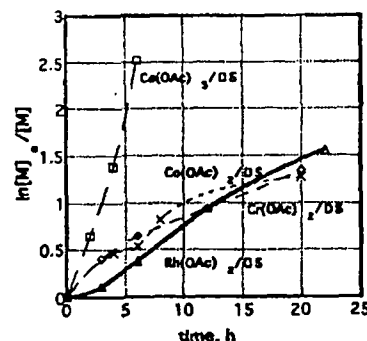


Fig. 1 Time-conversion plots in semilogarithmic coordinates for polymerization of MMA initiated by M<sup>II</sup>+(OAc)<sub>n</sub>/p-chlorobenzenediazonium tetrafluoroborate (1:1). [MMA]<sub>0</sub> = 5M, [I]<sub>0</sub> = 1.25×10<sup>-3</sup>M, THF/acetone (1:1), 40°C.

The highest polymerization rates were observed with the initiating system based on Ce(OAc)<sub>3</sub>/DS (90% conversion after 6 hours). With Rh(OAc)<sub>2</sub>/DS, an induction period was found during the first 2-3 hours.

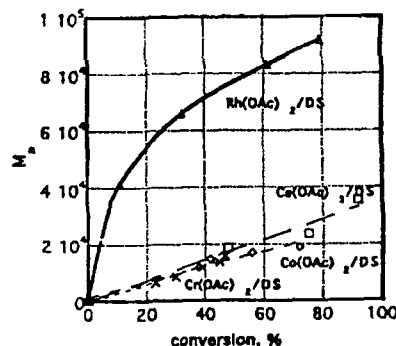


Fig. 2 M<sub>n</sub>-conversion dependence in polymerization of MMA initiated by M<sup>II</sup>+(OAc)<sub>n</sub>/p-chlorobenzenediazonium tetrafluoroborate (1:1). [MMA]<sub>0</sub> = 5M, [I]<sub>0</sub> = 1.25×10<sup>-3</sup>M, THF/acetone (1:1), 40°C.

Molecular weights increase monotonously with conversion. The highest values were observed with Rh(OAc)<sub>2</sub>/DS. It seems that the number of chains is constant for Ce, Co, and Cr-based initiating systems but it increases with Rh(OAc)<sub>2</sub>/DS. This observation together with induction periods (cf. Fig. 1) suggests slow initiation for Rh(OAc)<sub>2</sub>/DS. It must be noted that efficiency of initiation is very low for all of the discussed systems.

Despite slow initiation, Rh(OAc)<sub>2</sub>/DS yields polymers with the lowest polydispersities (1.2-1.45). Three other systems provide polymers with higher polydispersities, although molecular weights grow linearly with conversion, indicating low contribution of transfer. On the other hand, termination for these three systems should not be very important, judging from the kinetics (Fig. 1). Thus, the broader molecular weight distribution observed in Fig. 3, might be ascribed to slow exchange between dormant and active species.

Availability Codes

Dist	Availability
A-1	Special

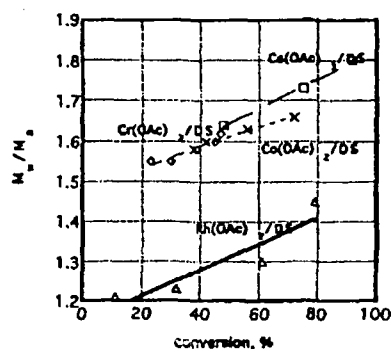


Fig. 3  $M_w/M_n$ -conversion dependence in polymerization of MMA initiated by  $Mt^{D+}(OAc)_n/p$ -chlorobenzendiazonium tetrafluoroborate (1:1).  $[MMA]_0 = 5M$ ,  $[I]_0 = 1.25 \times 10^{-1}M$ , THF/acetone (1:1),  $40^\circ C$ .

Polymerization of MMA with initiating systems based on metallocenes/diazonium salts proceeds faster and molecular weights are lower than with initiating systems based on acetates. Figure 4 presents  $M_n$  and  $M_w/M_n$ -conversion dependences.

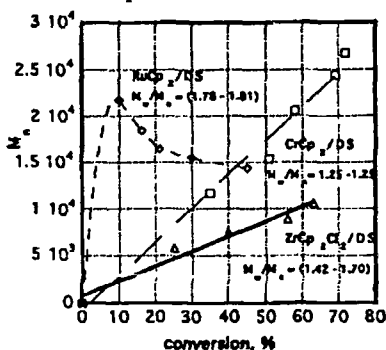


Fig. 4  $M_n$  and  $M_w/M_n$  - conversion dependence in polymerization of MMA with metallocenes/p-chlorobenzendiazonium tetrafluoroborate (1:1).  $[MMA]_0 = 5M$ ,  $[I]_0 = 1.25 \times 10^{-1}M$ , THF/acetone (1:1),  $40^\circ C$ .

The best control of molecular weights and the lowest polydispersities was observed with  $CrCp_2/DS$ . In the presence of  $RuCp_2/DS$  molecular weights decreased with conversion. This could be ascribed to transfer via  $\beta$ -H abstraction from the growing chains and the formation of ruthenium hydrides, capable of reinitiation.

Tacticities of PMMA prepared in systems initiated by metal acetates/metallocenes/diazonium salts are presented in Table 1. The microstructures are similar to those obtained in radical polymerization.

Table 1  
Microstructures of PMMA Prepared in Systems Initiated by Transition Metal Derivatives/DS

Initiator	(mm), %	(mr), %	(rr), %	p <sub>a</sub>
Rh(OAc) <sub>3</sub> /DS	2.1	26.7	71.2	1.75
Co(OAc) <sub>2</sub> /DS	2.6	35	62.4	1.27
Cr(OAc) <sub>3</sub> /DS	2.8	28.9	68.3	1.61
Ce(OAc) <sub>3</sub> /DS	3.2	31.4	65.4	1.46
ZrCp <sub>2</sub> Cl <sub>2</sub> /DS	1.7	24.8	73.5	1.9
RuCp <sub>2</sub> /DS	5.6	34	60.4	1.74
CrCp <sub>2</sub> /DS	2.4	31.1	66.5	1.32

a) p = persistence ratio = 2 (m)(r)/(mr)

In order to have a deeper insight into the mechanism of these polymerizations we have performed model trapping experiments and copolymerization studies. It seems that water and weak acids do not affect conversions, propagation rates and molecular weights, suggesting that the chains ends have radical rather than enolate structures. In copolymerization of MMA and styrene, reactivity ratios also similar to those calculated in any radical process. Radical species have been previously directly observed by EPR in a similar initiating system, based on lanthanum derivatives<sup>3</sup>.

Polymerization of methyl acrylate (MA) shows a behavior similar to MMA (Figs. 5, 6). The increase of molecular weights with conversion for MA is much less pronounced than for MMA polymerization. This can be ascribed to slower initiation and also to transfer reactions. The latter is most clearly noted when molecular weights decrease with conversion for  $Co(OAc)_2/DS$ . These side reactions lead to increase of polydispersities.

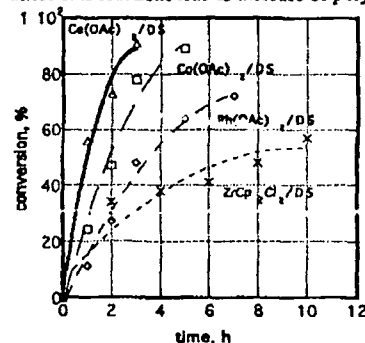


Fig. 5 Time-conversion plots in polymerization of methyl acrylate initiated by transition metal derivatives/p-chlorobenzendiazonium tetrafluoroborate (1:1).  $[MA]_0 = 5M$ ,  $[I]_0 = 1.25 \times 10^{-1}M$ , THF/acetone (1:1),  $40^\circ C$ .

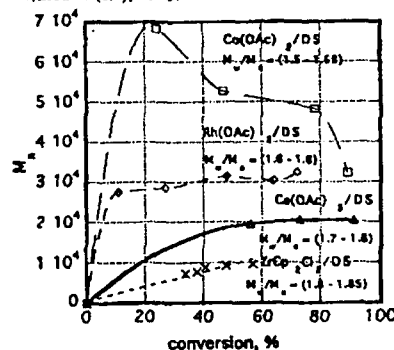


Fig. 6  $M_n$  ( $M_w/M_n$ ) - conversion dependence in polymerization of methyl acrylate initiated by transition metal derivatives/p-chlorobenzendiazonium tetrafluoroborate (1:1).  $[MA]_0 = 5M$ ,  $[I]_0 = 1.25 \times 10^{-1}M$ , THF/acetone (1:1),  $40^\circ C$ .

## Conclusions

Polymerization of acrylic monomers was redox initiated by mixtures (1:1) of transition metal derivatives (acetates, metallocenes) with arenediazonium salts. In most cases, molecular weights increase with the conversion and polydispersities are lower than in a typical radical or anionic polymerization at these temperatures. Trapping experiments and relative monomer reactivities based on copolymerization studies indicate that these polymerizations proceed via a radical mechanism. The improved polymerization control can be ascribed to an equilibrium between growing radicals and dormant persistent radicals.

## References

1. Lee, M., Utsumi, K., Minoura, Y., *J. Chem. Soc. Faraday Trans. 1*, 1979, 75(8), 1821
2. Mardare, D., Gaynor, S., Matyjaszewski, K., *ACS Polymer Preprints* 1994, 35(1), 700.
3. Sato, T., Toyosu, K., Tanaka, H., *Makromol. Chem.*, 1993, 194, 2797.
4. Citterio, A., Minisci, F., Albinati, A., Bruckner, S., *Tetrahedron Lett.*, 1980, 21, 2909.
5. Galli, C., *J. Chem. Soc. Perkin Trans. II*, 1982, 1139.

## Acknowledgements

Acknowledgement is made to the Office of Naval Research and to the National Science Foundation, via the support within Presidential Young Investigator Award to K. M., as well as to Du Pont, PPG Industries, and Xerox Corporation for the matching funds.