

60461-X
UNCLASSIFIED


SEP-91

Subject Category: METALLURGY AND CERAMICS

UNITED STATES ATOMIC ENERGY COMMISSION


THERMAL EXPANSION OF ZIRCONIUM AND
ZIRCONIUM-TIN ALLOYS UP TO 570°C

By
Marvin Moskowitz
L. W. Kates

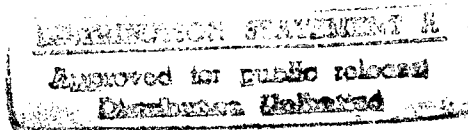

June 9, 1952

Metallurgical Laboratory
Sylvania Electric Products, Inc.
Bayside, New York



Technical Information Service, Oak Ridge, Tennessee

19970310 140

UNCLASSIFIED

EXEMPTION STATEMENT A

Work performed under Contract No. AT-30-1-Gen-366.

Date Declassified: November 18, 1955.

This report was prepared as a scientific account of Government-sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission makes any warranty or representation, express or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights. The Commission assumes no liability with respect to the use of, or from damages resulting from the use of, any information, apparatus, method, or process disclosed in this report.

This report has been reproduced directly from the best available copy.

Issuance of this document does not constitute authority for declassification of classified material of the same or similar content and title by the same authors.

Since nontechnical and nonessential prefatory material has been deleted, the first page of the report is page 5.

Printed in USA, Price 15 cents. Available from the Office of Technical Services, Department of Commerce, Washington 25, D. C.

THERMAL EXPANSION OF ZIRCONIUM AND ZIRCONIUM - TIN ALLOYS UP TO 570°C

By Marvin Moskowitz and L. W. Kates

I. INTRODUCTION

The present work was undertaken as part of the research being done in the design of a nuclear reactor for the Navy. Interest is centered on zirconium because of its low neutron absorption and high corrosion resistance, thus making it useful for cladding and various structural parts in a reactor. The addition of tin to zirconium, in proper amounts, produces an alloy with a higher resistance to corrosion than zirconium alone (1).

Various specimens of polycrystalline zirconium and zirconium-tin alloys were prepared for the purpose of obtaining useful engineering data on their thermal properties, specifically, thermal expansion.

From plots of length vs. temperature, as measured by a dial gauge mounted on an electric furnace and a thermocouple-potentiometer circuit, respectively, empirical equations of the second degree were derived by the method of least squares, one for each of the five samples of pressed and sintered zirconium and zirconium-tin powders. These equations represent the thermal linear expansion of the samples between 30° and 570°C and are of the form

$$L_t = L_0 (1 + at + bt^2) \quad (1)$$

where L_t is the length of the sample at any temperature, t , and L_0 the length at 0°C; a and b are constants.

From equation (1) may be derived the instantaneous linear coefficient at any temperature within the experimental range as well as an average coefficient between two temperatures. By differentiating L_t once with respect to t and dividing by L_0 , one obtains an instantaneous coefficient as follows:

$$\alpha_t = \frac{dL}{dt} \frac{1}{L_0} = a + 2bt \quad (2)$$

An estimation of relative error indicates that values of coefficients are correct to within 0.6%.

A comparison with the results of similar expansion work done on a sintered powder compact of pure zirconium shows agreement within 6% between values for the mean coefficient of expansion between 0 and 500°C. (2)

The relationship between tin content and linear coefficient at any temperature will be discussed in Part III.

II. EXPERIMENTAL

A. Materials

The samples were prepared from mixtures of -325 mesh, Grade C sponge zirconium hydride powder, mechanically pulverized, and -325 mesh metallic tin powder. They were pressed at 75 tsi with a die lubricated with stearic acid and sintered 10 hours at 1270°C in vacuo. The dimensions of the bars thus formed were roughly $1/3" \times 1/3" \times 5-1/3"$; all five bars were then machined down to cylindrical rods $4"$ long and $1/4"$ in diameter with small protruding pins $3/16"$ long centered at each end to facilitate mounting in the quartz tube holder.

B. Apparatus

Measurements were made with a standard quartz tube dilatometer equipped with a dial gauge calibrated in ten-thousandths of an inch. In operation, the specimen is seated and centered, by means of the end pin, inside and at the bottom of a quartz tube which is suspended inside an electric furnace and supported at the top by a clamp attached to the exterior of the furnace.

Another quartz tube of the same outside diameter as the specimen fits over the upper end of the specimen and extends upward and slightly beyond the outer tube. Upon the top of this inner tube rests the dial gauge. A chromel-alumel thermocouple resting in a small transverse hole bored at the midpoint of the specimen and led through the tubes to a potentiometer indicates specimen temperature.

The reading limit of the dial gauge is $\pm 0.0001"$. Temperatures may be determined to $\pm 1.5^\circ\text{C}$.

III. PROCEDURE AND RESULTS

The heating rate control of the furnace was set at approximately 2.5°C per minute; the average cooling rate was appreciably lower. A constant stream of argon was passed over the specimen during both heating and cooling to avoid possible contamination. In spite of this, all the specimens lost their silvery appearance and became quite darkened after the first few runs. It is assumed that the data obtained were not affected by this thin oxide layer.

Dial gauge and potentiometer readings were taken at approximately 50-degree intervals.

III. PROCEDURE AND RESULTS (Cont'd.)

Anywhere from two to six runs were made on each specimen, depending upon the repeatability of the length vs. temperature plot. Reasonable repeatability of the curves was achieved after what were assumed to be stresses due to machining were relieved by reheating. Cooling curves were disregarded, insofar as calculations were concerned, because of poor precision of the dilatometer during the cooling cycle as a result of a mechanical defect in the dial gauge.

The final heating curve for each sample was graphically corrected for the expansion of the quartz tube and used for a determination of a second degree equation - equation (2) - by the method of least squares. The equations thus derived apply in the temperature range between 30° and 570°C and are listed in Table I.

Expansion curves for the various materials are given in Fig. 1. Values of $\Delta L/L_0$ were calculated directly from equation (1). By simple manipulation, this equation may be put into the required form.

$$L_t = L_0 + L_0 (at + bt^2)$$

$$\frac{L_t - L_0}{L_0} = at + bt^2$$

where

$$L_t - L_0 = \Delta L$$

Thus

$$\frac{\Delta L}{L_0} = at + bt^2 \quad (3)$$

TABLE I

| <u>Composition of Sample</u> | <u>Equation</u> |
|------------------------------|--|
| 100% Zr, 0% Sn | $L_t = 4.0040 (1 + 5.99 \times 10^{-6}t + 1.55 \times 10^{-9}t^2)$ |
| 99% Zr, 1% Sn | $L_t = 3.9986 (1 + 5.98 \times 10^{-6}t + 1.86 \times 10^{-9}t^2)$ |
| 97% Zr, 3% Sn | $L_t = 3.9947 (1 + 6.31 \times 10^{-6}t + 1.29 \times 10^{-9}t^2)$ |
| 95% Zr, 5% Sn | $L_t = 4.0058 (1 + 6.04 \times 10^{-6}t + 2.62 \times 10^{-9}t^2)$ |
| 93% Zr, 7% Sn | $L_t = 3.9883 (1 + 6.70 \times 10^{-6}t + 1.84 \times 10^{-9}t^2)$ |

L_t is expressed in inches if t is in degrees centigrade.

III. PROCEDURE AND RESULTS (Cont'd.)

The overall linear expansion per unit length increases with tin content over the temperature range studied, as may be seen from Fig. 1.

The variation of instantaneous coefficient with temperature is shown in Fig. 2. This is actually a plot of the slopes of the curves of Fig. 1 against temperature. As may be seen, the instantaneous coefficient does not always increase with tin content.

Metallographic analysis reveals the location of the tin-rich phase at the grain boundaries. Fig. 3 shows the five specimens under polarized light magnified 200x. The tin phase shows up as small white areas at the grain boundaries.

IV. CONCLUSIONS

The experimental data obtained from thermal linear expansion measurements on zirconium and zirconium-tin alloy specimens containing 0%, 1%, 3%, 5%, and 7% tin by weight were used to derive separate second degree equations for each specimen, relating length and temperature. On the basis of these equations the following conclusions may be drawn regarding the expansion coefficients:

1. The linear expansion coefficients increase with temperature for all the specimens tested.
2. The mean coefficients increase with tin content over the temperature range studied but the instantaneous coefficients do not show the same uniformity.
3. The data obtained for the 0% tin specimen agree within 6% with previously published data on a sintered powder compact of pure zirconium.

BIBLIOGRAPHY

- (1) M. C. Udy, H. L. Shaw, F. W. Boulger, BMI-711, Battelle Memorial Institute, 1951, p. 67.
- (2) Ibid., p. 35.

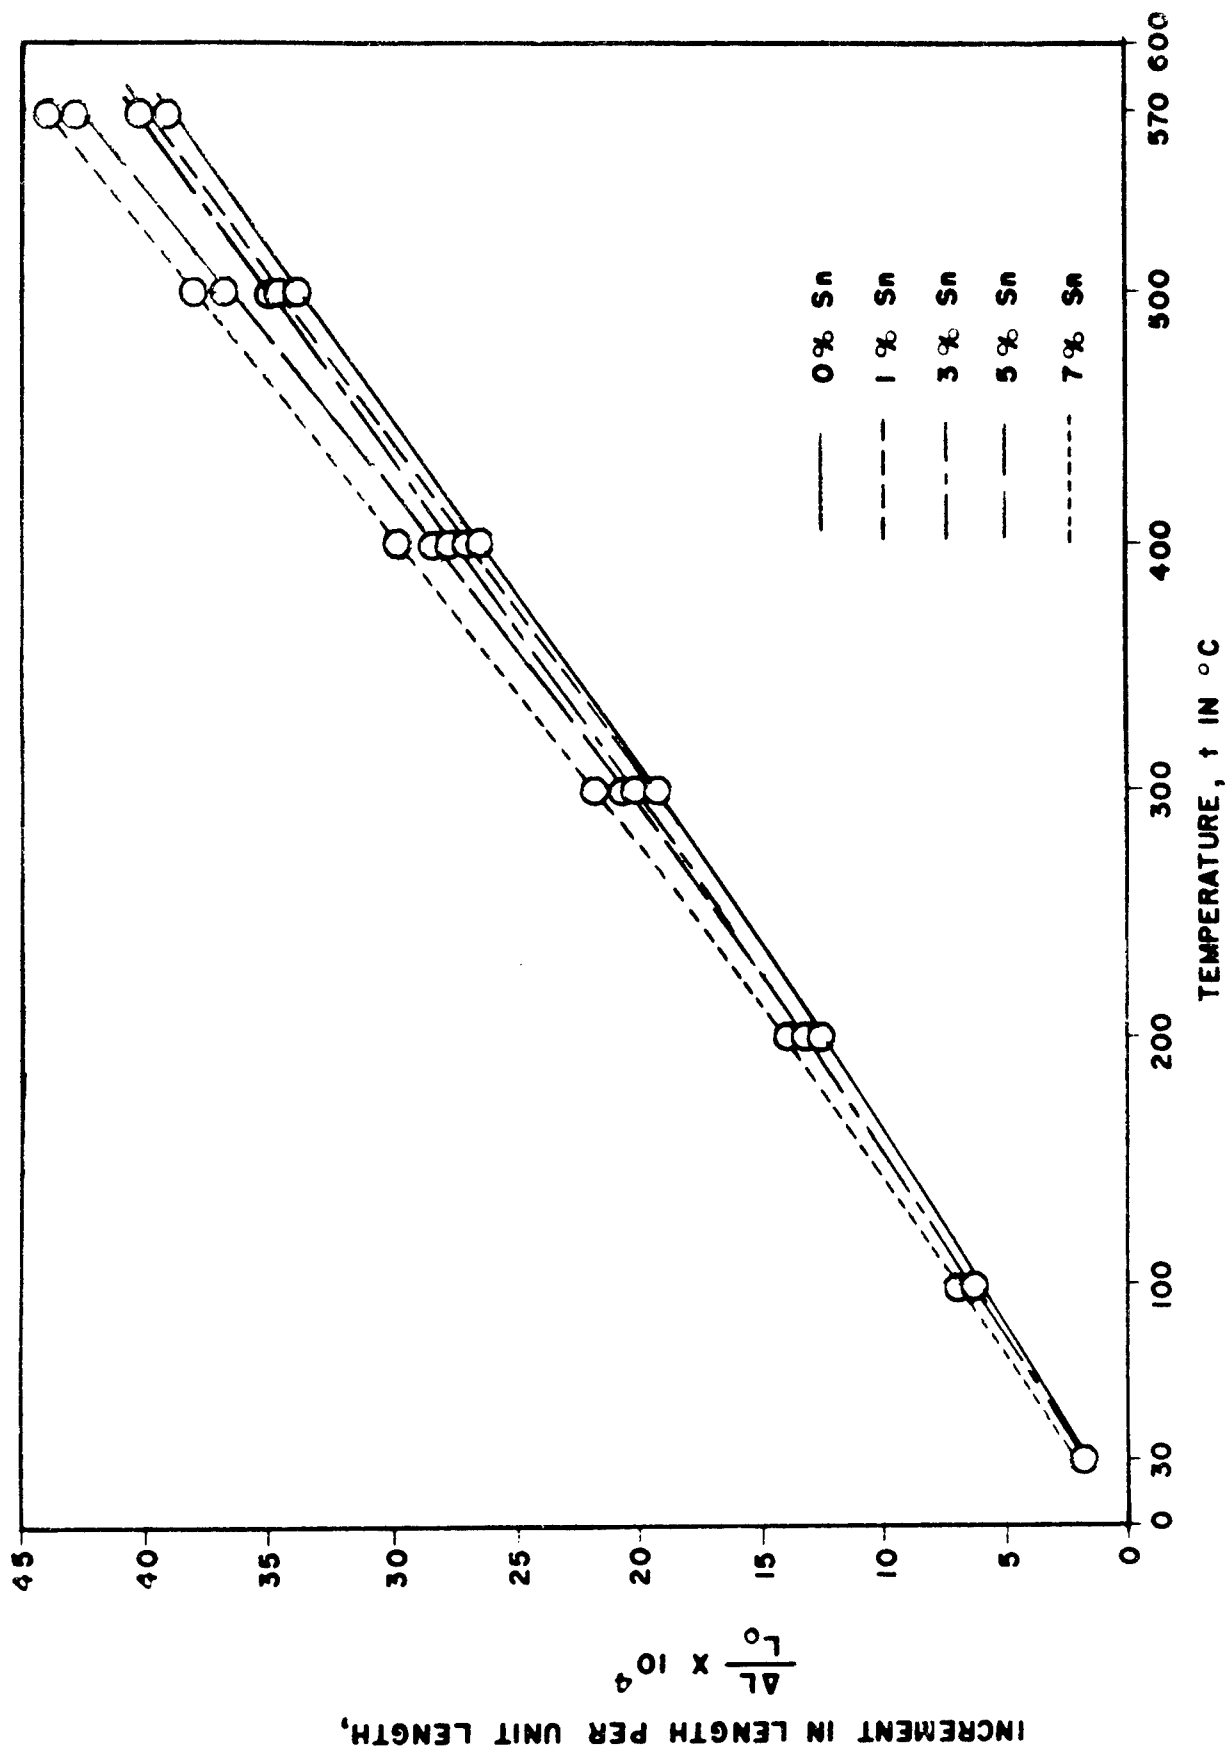


Fig. 1 Linear thermal expansion of zirconium and zirconium-tin alloys.


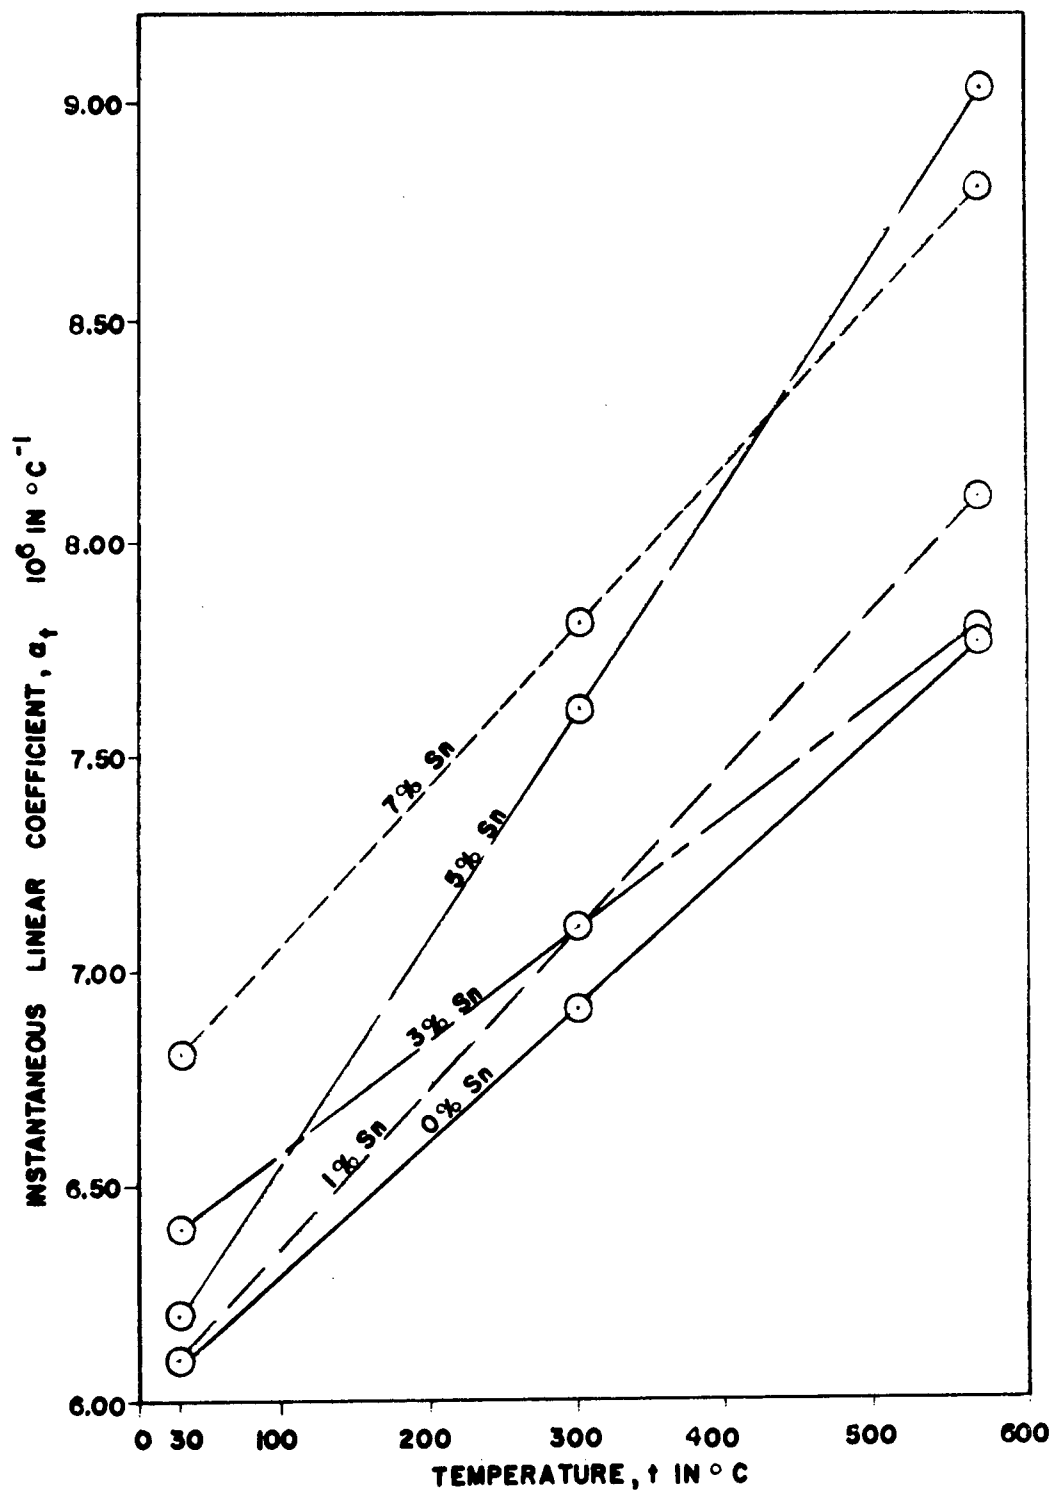


Fig. 2 Variation of instantaneous linear thermal coefficient of expansion of zirconium and zirconium-tin alloys with temperature.



(a)

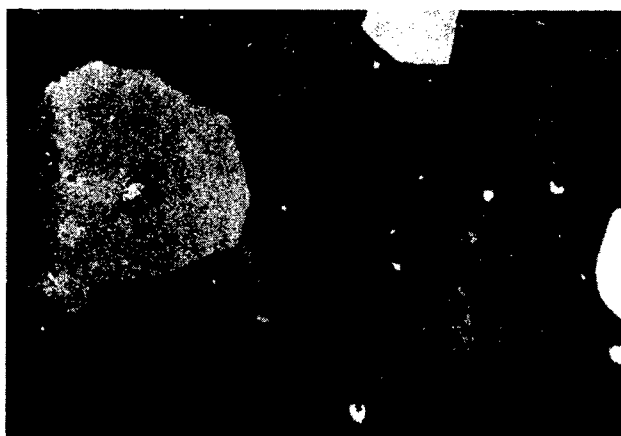

(b)



(c)



(d)



(e)

Fig. 3 Photomicrographs of Zirconium and Zirconium-Tin Alloys.
Polarized Light. 200X