

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing this collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. **PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.**

1. REPORT DATE (<i>DD-MM-YYYY</i>) 03/15/2010	2. REPORT TYPE Final	3. DATES COVERED (<i>From - To</i>) 06/15/2009 - 06/14/2010
---	--------------------------------	---

4. TITLE AND SUBTITLE A review of recent research on mechanics of multifunctional materials and structures	5a. CONTRACT NUMBER
	5b. GRANT NUMBER FA9550-09-1-0506
	5c. PROGRAM ELEMENT NUMBER

6. AUTHOR(S) Dr. Ronald F. Gibson	5d. PROJECT NUMBER
	5e. TASK NUMBER
	5f. WORK UNIT NUMBER

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of Nevada, Reno Dept. of Mechanical Engineering MS-312 Reno, NV 89557	8. PERFORMING ORGANIZATION REPORT NUMBER
--	---

9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) Dr. Byung-Lip Lee AFOSR/NA 875 N. Randolph St., Rm. 3112 Arlington, VA 22203	10. SPONSOR/MONITOR'S ACRONYM(S) AFOSR/NA
	11. SPONSOR/MONITOR'S REPORT NUMBER(S)

12. DISTRIBUTION / AVAILABILITY STATEMENT Public Release

13. SUPPLEMENTARY NOTES

14. ABSTRACT
This report is an attempt to identify the topics that are most relevant to multifunctional materials and structures and review representative journal publications that are related to those topics. Articles covering developments in both multiple structural functions and integrated structural and nonstructural functions since 2000 are emphasized. Structural functions include mechanical properties like strength, stiffness, fracture toughness, and damping, while nonstructural functions include electrical and/or thermal conductivity, sensing and actuation, energy harvesting/storage, self-healing capability, and electromagnetic interference (EMI) shielding. Many of these recent developments are associated with polymeric materials and corresponding advances in nanomaterials and nanostructures, as are many of the articles reviewed. The report concludes with a discussion of recent applications of multifunctional materials and structures. Several suggestions regarding future research needs are also presented.

15. SUBJECT TERMS

16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES 42	19a. NAME OF RESPONSIBLE PERSON Dr. Ronald F. Gibson
a. REPORT	b. ABSTRACT	c. THIS PAGE			19b. TELEPHONE NUMBER (<i>include area code</i>) 775-784-1489

Table of Contents

Nomenclature	2
1. Introduction	3
2. Multiple structural functions	6
2.1 Composite structural materials	6
2.2 Hybrid multiscale composite structural materials	7
3. Integrated structural and nonstructural functions	12
3.1 Electrical and/or thermal conductivity	13
3.2 Sensing and actuation	15
3.3 Energy harvesting/storage	21
3.4 Self-healing capability	25
3.5 Electromagnetic interference (EMI) shielding	28
4. Recent applications of multifunctional materials and structures	29
5. Concluding remarks	35
Acknowledgements	36
References	36

Nomenclature

A	surface area of spherical particle
C_D	drag coefficient
C_L	lift coefficient
E_B	nominal stored battery energy
E_i	incident electric field
E_t	transmitted electric field
H_i	incident magnetic field
H_t	transmitted electric field
k_s	piezoelectric coupling coefficient for sensing
k_a	piezoelectric coupling coefficient for actuation
k_c	electrical conductivity of composite
k_f	electrical or thermal conductivity of filler
k_m	electrical or thermal conductivity of matrix
$K_{Ic_{healed}}$	Mode I fracture toughness for healed specimen
$K_{Ic_{virgin}}$	Mode I fracture toughness for virgin specimen
$P_{c_{healed}}$	critical fracture load for healed Mode I fracture specimen
$P_{c_{virgin}}$	critical fracture load for virgin Mode I fracture specimen
S	wing planform area
SE	EMI shielding effectiveness
t_E	flight endurance time
U_e	electrical (dielectric) energy density
V	volume of spherical particle
W_B	battery subsystem weight
W_{PL}	payload subsystem weight

W_{PR}	propulsion subsystem weight
W_S	structure subsystem weight
W_m	mechanical (strain) energy density
α	conductivity exponent
η	crack healing efficiency
η_B	efficiency factor for battery
η_P	propeller efficiency
ρ	air density
φ	concentration of carbon nanotubes
φ_c	critical concentration of carbon nanotubes, or percolation threshold

1. Introduction

The number of publications dealing with various aspects of the mechanics of multifunctional materials and structures has increased markedly in recent years. Figure 1 shows how the number of English language refereed journal articles in multifunctional materials and structures has steadily increased since 2000, based on data collected from the Engineering Village© web-based information service.

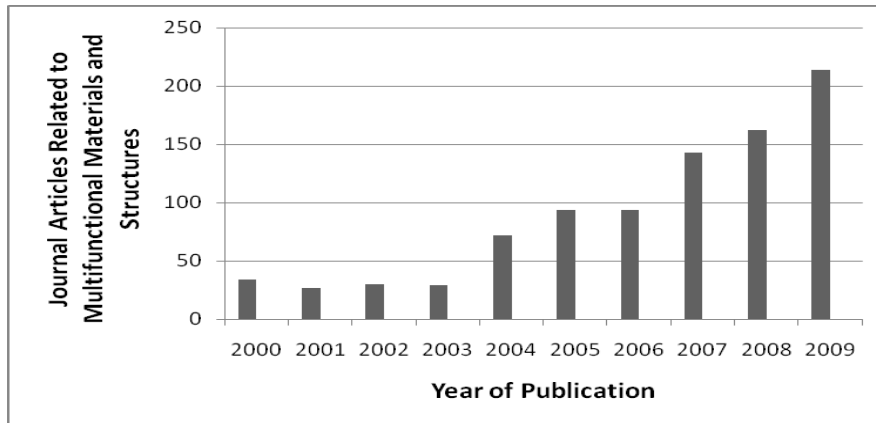


Figure 1. Recent English language refereed journal publications related to multifunctional materials and structures. Data collected from Engineering Village© web-based information

Along with the increase in the number of publications in this area comes a need for a comprehensive review article, and the objective of this paper is to address this need. The emphasis of the publications surveyed will be on the mechanics aspects, although the multidisciplinary nature of the topic will lead to the inclusion of some publications on relevant

disciplines such as materials science, thermodynamics, and electronics. In addition, the vast majority of the surveyed articles deal with polymers and polymer composites. Due to the large number of articles involved, and the lack of electronic access to many conference proceedings, the emphasis of this review is on the more accessible refereed journal articles. It was not practical to cover all of these articles, and since some articles had already been covered by previous related review articles, an attempt was made to select representative articles in each of the relevant categories. According to Fig. 1, most of the relevant articles have been published since 2000, so that is the focus of this review.

The increased interest in multifunctional materials and structures is driven by the need for the development of new materials and structures that simultaneously perform (a) multiple structural functions, (b) combined non-structural and structural functions, or (c) both. One example of a multifunctional structure of type (a) would be a composite structure that has high strength, high stiffness, high fracture toughness and high damping. An example of type (b) would be a load-bearing structure that has the capability of providing its own noise and vibration control, self-repair, thermal insulation, and energy harvesting/storage, whereas an example of type (c) would be a structure combining the functions of both type (a) and type (b). Most of the recent developments in multifunctional materials and structures tend to be of type (b).

Multifunctional materials are necessarily composite materials, and the strong growth in the use of composites has been greatly influenced by multifunctional design requirements. The traditional approach to the development of structures is to address the load-carrying function and other functional requirements separately, resulting in a suboptimal load-bearing structure with add-on attachments which perform the non-structural functions with the penalty of added weight. Recently, however, there has been increased interest in the development of load-bearing materials and structures which have integral non-load-bearing functions, guided by recent discoveries about how multifunctional biological systems work.

Due to the interdisciplinary nature of multifunctional materials and structures, and the need to avoid duplication in the current review, it is appropriate to cite several relevant previous review articles. For example, Baur and Silverman [1] reviewed the challenges and opportunities in

multifunctional nanocomposite aerospace structures, while Ye, et al. [2] reviewed developments in the application of artificial intelligence to functionalize composite airframes. By definition, a multifunctional material must be a composite, and it is becoming increasingly apparent that nanostructured composites can produce and/or enhance multifunctionality in ways that conventional composites could not. For example, Thostenson, et al. [3] and Chou, et al. [4] reviewed recent advances related to the science and technology of carbon nanotubes and their composites, Breuer and Sundararaj [5] reviewed recent studies on polymer/carbon nanotube composites, Li, et al. [6] surveyed the recent advances related to the use of carbon nanotubes and their composites as sensors and actuators, while Gibson, et al. [7] reviewed recent publications dealing with vibrations of carbon nanotubes and their composites, and Sun et al. [8]. reviewed articles dealing with various types of energy absorption in nanocomposites. With the addition of very small amounts of carbon nanotubes, nonconducting polymers and polymer composites can be transformed to conducting materials, thus enhancing their multifunctionality. Accordingly, Bauhofer and Kovacs [9] have reviewed relevant research on electrical percolation in carbon nanotube polymer composites. Modeling and analysis of functionally graded materials (FGM) have been reviewed by Birman and Byrd [10]. The field of structural health monitoring (SHM) is highly relevant here, and several review articles have appeared recently. Montalvao, et al. [11] reviewed vibration-based SHM of composite materials, while a similar review with emphasis on composite delamination identification had been published earlier by Zou, et al. [12]. Recent developments in self-healing polymeric materials were reviewed by Wu, et al. [13]. Articles on energy harvesting for sensor networks in SHM were reviewed by Park, et al. [14]. Piezoelectric materials are often utilized for energy harvesting, and publications on this topic have been reviewed by Sodano, et al. [15], Anton and Sodano [16], and Cook-Chennault, et al. [17]. Closely related to SHM is the study of shape memory polymers (SMP), and reviews of recent advances in SMP have been published by Ratna and Karger-Kocsis [18]. Gibson, et al.[19] edited the Proceedings of the 2008 SAMPE Fall Technical Conference entitled “Multifunctional Materials: Working Smarter Together”. Lau, et al. [20] have archived selected papers from the 2008 International Conference on Multifunctional Materials and Structures (MFMS 08), which was held in Hong Kong.

2. Multiple structural functions

2.1 Composite structural materials

Among the most important structural functions that a system can provide are stiffness, strength, fracture toughness, ductility, fatigue strength, energy absorption, damping, and thermal stability. Although structural weight is not a function, it is an extremely important design consideration which has driven more designs towards lightweight composite materials in recent years. With conventional structural materials, it has been difficult to achieve simultaneous improvement in multiple structural functions, but the increasing use of composite materials has been driven in part by the potential for such improvements. For example, it has been shown that simultaneous improvements in vibration damping and fracture toughness in composite laminates are made possible by incorporating polymeric interleaves between the composite laminae [21]. However, this is only true if the interleaf thickness is less than a critical value – further increases in interleaf thickness cause the fracture toughness to drop off while the damping keeps increasing.

The use of nanoreinforcements in polymer composites has produced unprecedented improvements in mechanical properties of the composites. Koratkar, et al. [22] measured greater than 1000% increases (Fig. 2) in the loss modulus of polycarbonate (PC) without significant reductions in the storage modulus when the PC was enhanced by 2 wt% of single-walled carbon nanotubes (SWNTs).

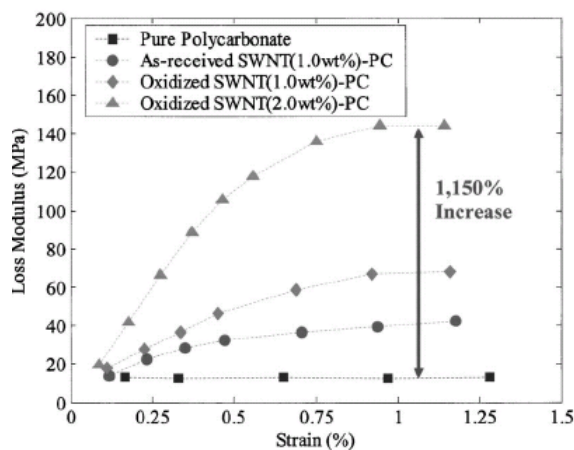


Figure 2. Loss moduli for pure PC and several SWNT/PC nanocomposites at different strain levels [22].

It was hypothesized that frictional sliding at the SWNT/PC interfaces was the reason for the enhanced energy dissipation. This hypothesis is supported by the analysis of Zhou, et al. [23], who developed a model for the frictional sliding damping mechanism based on interfacial “stick-slip” frictional motion between the nanotubes and the polymer matrix. Rajoria and Jalili [24] reported that multi-walled carbon nanotubes (MWNTs) were more effective than SWNTs in improving damping of epoxy, but there was no significant effect on the storage modulus. Another way to incorporate the improved damping associated with nanotube reinforcement is to embed nano-enhanced polymer film sub-layers within a multifunctional composite laminate [25,26].

By mixing silica microparticles and epoxy in the right proportions, it is possible to simultaneously increase strength and modulus of the resulting composite while reducing its coefficient of thermal expansion (CTE) [27]. These are all desirable changes, but if the volume fraction of silica is increased too much, the strength will start to drop due to particle agglomeration, poor particle dispersion and reduced silica/epoxy interfacial strength. Even with composites, it is not always possible to simultaneously improve several properties - in some cases, modifications to composites lead to major improvements in some properties while causing minor reductions in other properties. For example, the incorporation of rubber microparticles in the epoxy matrix of a glass fiber reinforced epoxy composite improved the tensile fatigue life of the composite by a factor of three while causing only a 5.2% reduction in the tensile strength and a 12.7% reduction in the elastic modulus [28].

2.2 Hybrid multiscale structural composite materials

There are increasing reports in the literature that significant improvements of multiple structural functions can be achieved with new hybrid multiscale composites which incorporate nanoscale reinforcements as well as conventional micron scale fiber or particle reinforcements. For example, while fiber-dominated properties (i.e., longitudinal tensile strength and elastic modulus) of conventional unidirectional polymer composites with micron size fiber reinforcements are excellent, the corresponding matrix-dominated transverse tensile strength and

longitudinal compressive strength properties are often poor. However, these traditionally poor properties can be significantly improved by (a) replacing the neat resin polymer matrix with a nanocomposite matrix (see Fig. 3 from Vlasveld, et al. [29]), and/or by (b) growing nanoreinforcements like carbon nanotubes on the surface of the fibers (see Fig. 4 from Zhao, et al. [30]).

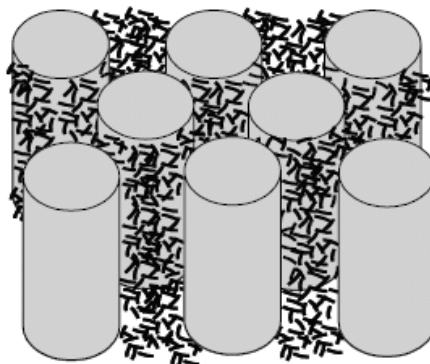


Figure 3. Nanoparticle reinforcement of the matrix in a unidirectional fiber composite [29].

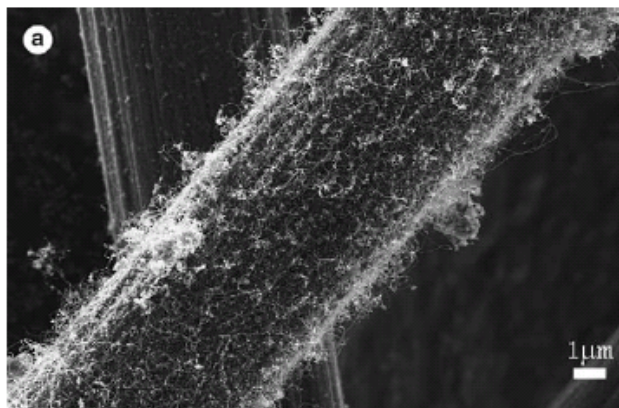


Figure 4. Multiwalled carbon nanotubes grown on the surface of carbon fibers [30].

In one example of approach (a), Uddin and Sun [31] reported that when a silica nanoparticle-enhanced epoxy was used as the matrix material in a unidirectional E-glass/epoxy composite, the longitudinal compressive strength and modulus were both significantly improved. Minimization of particle agglomeration and resulting improved dispersion of silica nanoparticles

in the epoxy matrix due to the use of a sol-gel process based on the use of organosilicasol (colloidal silica in organic solvent) is believed to be the primary reason for the improvements. More recent research by the same authors extended the approach to hybrid multiscale composites containing not only the silica nanoparticles from the sol-gel process but alumina nanoparticles and carbon nanofibers (CNF) in an epoxy matrix [32]. As shown in Figs. 5-7, simultaneous improvements of at least 30% in modulus, strength and strain at break are possible with several types of these hybrid nanocomposites,

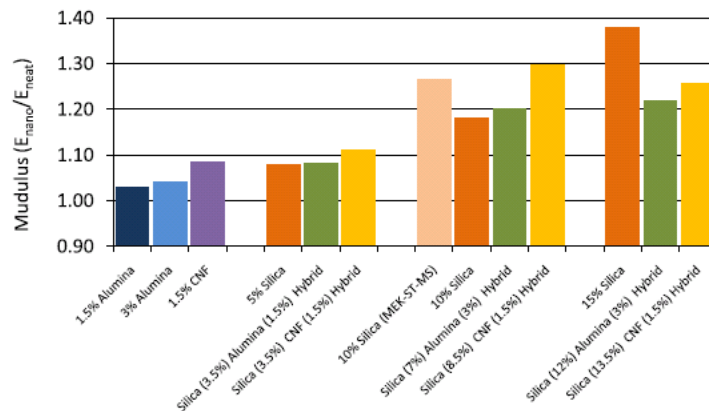


Figure 5. Flexural moduli of different nanocomposites at various particle loadings [32].

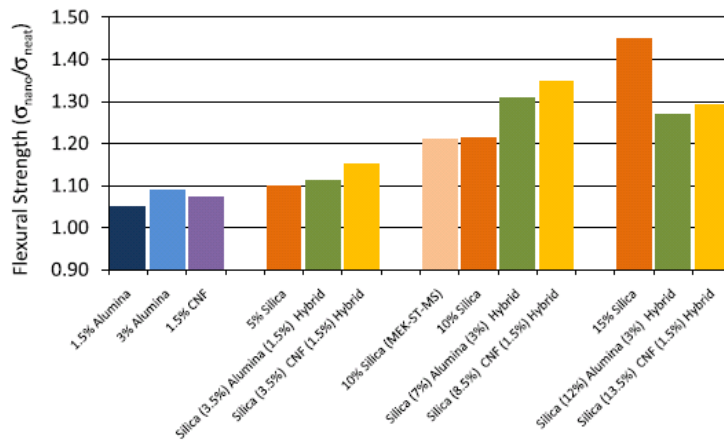


Figure 6. Flexural strengths of different nanocomposites at various particle loadings [32].

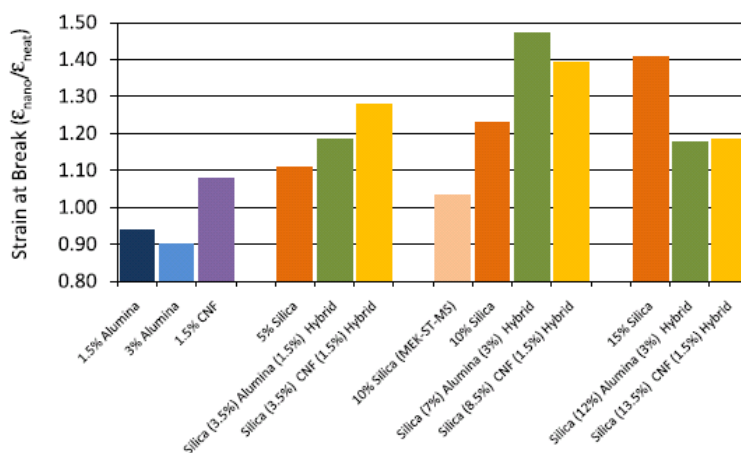


Figure 7. Flexural strains at break of different nanocomposites at various particle loadings [32].

Similarly, Liu, et al.[33] and Zhang, et al. [34] found that Young's modulus, tensile strength and fracture toughness of epoxy all simultaneously improved with the addition of sol-gel-formed nanosilica particles, and that the dispersion of the particles was excellent. Manjunatha, et al. [35] observed that the addition of 10 wt% sol-gel-formed nanosilica to the epoxy matrix resulted in simultaneous improvements of 4.4% in tensile strength, 7.4% in tensile modulus and a factor of 2 to 3 in tensile fatigue life of a glass fabric-reinforced epoxy composite. The presence of the nanoparticles was believed to suppress matrix cracking and reduce delamination growth rate, thus improving the fatigue life. Since hybrid multiscale composites typically have reinforcement sizes ranging from the micron scale to the nano scale, it is essential to understand the effects of particle size on the resulting composite properties. Important observations regarding such effects were reported by Cho, et al. [36], who measured modulus and strength of vinyl ester polymer matrix composites containing spherical alumina particles or glass beads, with particle sizes ranging from 0.5 mm down to 15 nm. It was found that the Young's modulus was not affected by varying particle sizes in the micron range, but as the particle size was reduced in the nano range, the Young's modulus increased with decreasing particle size. The tensile strength increased with decreasing particle sizes in both micron and nano ranges as long as particle agglomeration was avoided. Cho and Sun [37] later used molecular dynamics simulation to show that if the polymer-nanoparticle interaction strength is greater than the polymer-polymer interaction strength, the polymer density near the polymer-nanoparticle interface and the Young's modulus of the nanocomposite both increase significantly with reduced particle size.

More research is needed about particle size effects on both structural and nonstructural properties of nanocomposites and hybrid multiscale composites. This is particularly true for analytical modeling, since most of the publications to date involve experimental work.

Approach (b) which involves the growth of nanotubes on the surfaces of micron-sized fibers has also been the subject of numerous investigations. Thostenson, et al. [38] grew carbon nanotubes (CNTs) on the surface of carbon fibers using chemical vapor deposition (CVD), then conducted single fiber fragmentation tests of the modified carbon fibers in an epoxy matrix to determine the fiber/matrix interfacial shear strength. It was found that the interfacial shear strength of the modified carbon fibers was 15% greater than that of the baseline carbon fibers. Veedu, et al. [39] also used CVD to grow aligned CNT forests perpendicular to the surface of 2D woven SiC fabric cloth consisting of micron size SiC fibers. The fabrics were then infiltrated with epoxy resin and stacked to form a 3D composite. Compared with the baseline composite, the 3D composite was found to exhibit simultaneous and significant improvements in the Mode I and Mode II fracture toughnesses, the flexural modulus, the flexural strength, the flexural toughness, the coefficient of thermal expansion, the thermal conductivity and the electrical conductivity. This is a true multifunctional composite combining structural and nonstructural functions, and will be discussed further in the next section. Further studies and applications of aligned CNT forests to conventional fiber composites have been reported by Wardle and his colleagues [40-44], who focused on the use of the aligned CNT forests to improve interlaminar strength and toughness. These are major concerns about conventional composite laminates because of the weak matrix resin-rich regions that exist between the composite laminae. As shown in Fig. 8, vertically aligned CNT forests can bridge and strengthen this interlaminar region [41]. More specifically, the authors reported that the CNT modified interfaces increased the Mode I interlaminar fracture toughness of aerospace grade carbon/epoxy laminates by a factor of 1.5 to 2.5 and the corresponding Mode II value by a factor of 3. Analytical modeling of fracture toughness of the CNT-modified laminates based on the crack closure technique for fiber bridging was reported later in [43]. The so-called “fuzzy fiber” (CNTs grown on carbon fibers) concept applied to composite laminates can provide both interlaminar and intralaminar reinforcement as illustrated in Fig. 9 [44].

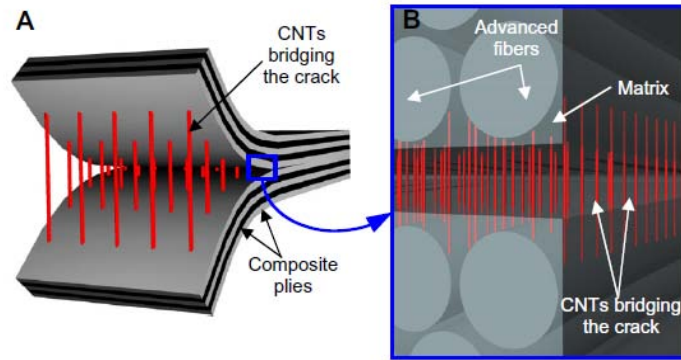


Figure 8. Use of aligned CNT forests to strengthen interlaminar region in composite laminates [41].

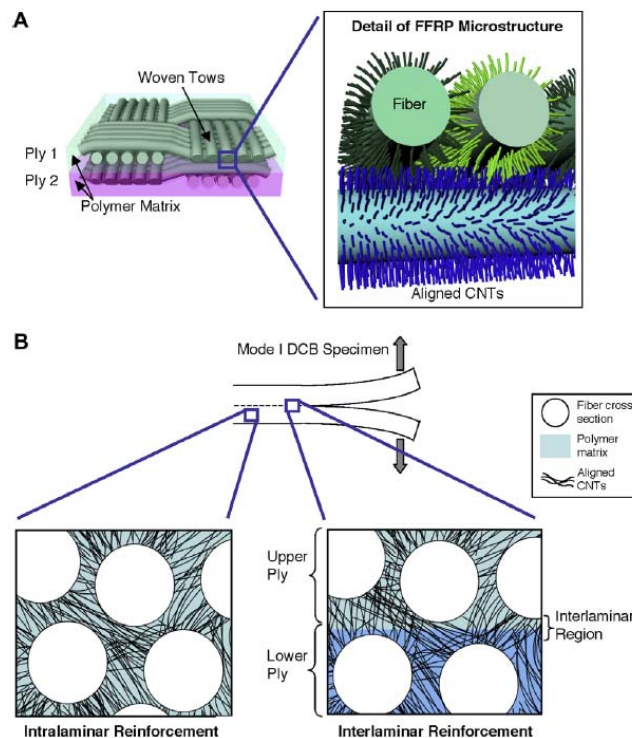


Figure 9. Illustration of fuzzy fiber reinforced plastic (FFRP). (A) radially aligned CNTs grown on advanced fiber cloth (B) CNT intralaminar and interlaminar reinforcement [44].

3. Integrated structural and nonstructural functions

As indicated in the previous section, the development of nanocomposites and hybrid multiscale composites containing both conventional micron level reinforcements and nano level reinforcements has made it possible to achieve simultaneous improvements in not only multiple

structural functions, but multiple nonstructural functions as well. This section focuses on several important nonstructural functions, including electrical and/or thermal conductivity, sensing and actuation, energy harvesting/storage, self-healing capability, and electromagnetic interference (EMI) shielding.

3.1 Electrical and/or thermal conductivity

Among the most important nonstructural functions that a structure may need are electrical and thermal conductivity, but the most widely used composites have polymer matrix materials, which are typically poor conductors. One very important application of polymer composites where electrical conductivity is required is in aircraft structures, where nonconducting structures may be damaged by lightning strikes. Here, conductive polymer nanocomposites are being investigated as possible replacements for nonconducting polymer matrix materials. This would eliminate the need for add-on metallic conductors, which are too heavy and may be difficult to repair [45]. Enhanced thermal conductivity of composites is important for cooling of electronic circuits and propulsion systems. The structural advantages of nanocomposites have already been summarized in the previous section, and there is abundant evidence in the literature of simultaneous improvements in mechanical and electrical properties of nanocomposites [46-49].

It turns out that very small concentrations of carbon nanotubes or other conducting nanoreinforcements in polymers lead to disproportionately large improvements in the electrical conductivity of the nanocomposite. For example, Fig. 10 shows that the electrical conductivity of CNT/epoxy nanocomposites increases by nearly 6 decades when the CNT concentration is increased by only 2 decades [9]. The “percolation threshold”, φ_c , which is the CNT concentration in the polymer that characterizes the insulator-conductor transition, is only 0.04 wt% in this case. Percolation theory accurately describes this transition by the equation

$$k_c = (\varphi - \varphi_c)^\alpha \quad (1)$$

Sandler, et al. [50] reported ultra-low percolation thresholds as low as 0.0025 wt% for aligned MWNT/epoxy nanocomposites. The percolation threshold for CNTs in polymer matrix materials

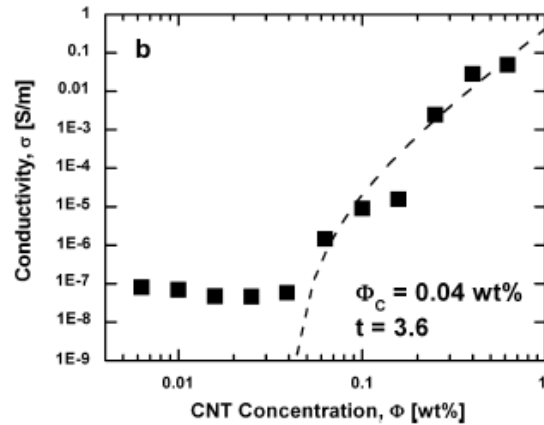


Figure 10. Electrical conductivity of CNT/epoxy nanocomposites at various CNT concentrations. Percolation threshold is 0.04 wt% [9].

is so low because the extremely high aspect ratios of CNTs make it relatively easy for a contiguous conducting path or percolation network to form along the tangled CNTs in the insulating polymer matrix. Fig. 11 from Li, et al. [51] shows how the percolation threshold decreases with increasing CNT aspect ratio.

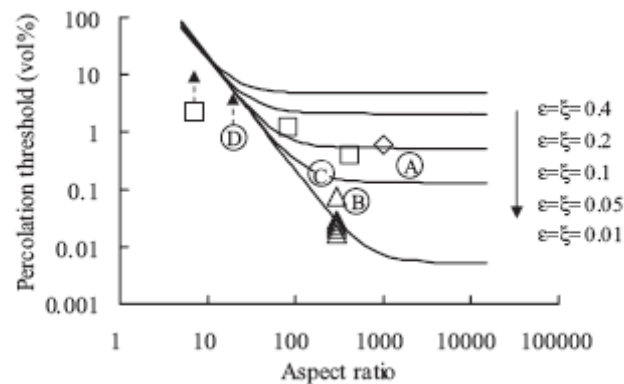


Figure 11. Effect of CNT aspect ratio on percolation threshold for CNT nanocomposites with varying dispersion states [51].

Since processing typically breaks up CNTs into shorter lengths, it is important to develop processes which preserve the high aspect ratios of CNTs, thus insuring the desired low percolation thresholds. Thostenson, et al. [52] reported that a 3-roll mill process induces intense shear mixing of a CNT/vinyl ester nanocomposite while preserving the high aspect ratios of the CNTs. Photomicrographs show that CNTs are wavy, but most analytical models are based on the assumption that the CNTs are straight. The importance of waviness was confirmed by Li, et al.

[53], who used Monte Carlo simulations to show that the electrical conductivity of composites with wavy nanotubes is less than that of composites with straight nanotubes.

Although the thermal conductivity of CNT/polymer nanocomposites increases with the increasing CNT concentration, the increase is gradual and there is no sharp insulator-conductor transition or percolation threshold as in electrical conductivity [54]. According to Shenogina, et al. [54], the difference lies in the conductivity ratio k_f/k_m . For thermal transport, even for very conductive, high aspect ratio CNTs, k_f/k_m is only about 10^4 , but for electrical transport, k_f/k_m can be as much as 10^{12} - 10^{16} . As a result, electrical transport is dominated by the percolating CNT network, whereas thermal transport is strongly influenced by the polymer matrix. Although there is a lack of a percolation threshold for thermal conductivity in CNT/polymer composites, small amounts of CNTs still lead to disproportionate increases in composite thermal conductivity. For example, Biercuk, et al. [55] found that 1 wt% SWNTs in epoxy resulted in a 125% increase in thermal conductivity at room temperature, Bonnet, et al. [56] measured a 55% increase in thermal conductivity for a 7 wt% SWNT/PMMA composite, and Kim, et al. [57] reported a 57% increase in thermal conductivity by adding 7 wt% MWNTs in phenolic resin. However, since higher filler loadings are required to create significant improvements in thermal conductivity of polymers, this may lead to processing issues. For example, Ganguli, et al. [58] were able to achieve a 28-fold increase in thermal conductivity of epoxy by adding 20 wt% chemically functionalized and exfoliated graphite flakes, but graphite loading levels greater than 4 wt% were found to increase the viscosity of the mixture beyond the desirable processing window for the vacuum-assisted-resin-transfer molding (VARTM) process. In some applications, only small amounts of CNTs are needed to produce acceptable thermal conductivity. For example, Sihn, et al. [59] found that the through-thickness thermal conductivity of epoxy adhesive joints can be increased by several orders of magnitude when aligned MWNT “nanograss” is incorporated in the epoxy adhesive (Fig. 12).

3.2 Sensing and actuation

Sensing and actuation are two closely related nonstructural functions, and in many cases, the same material or device can be used for both functions, as well as for other functions like energy

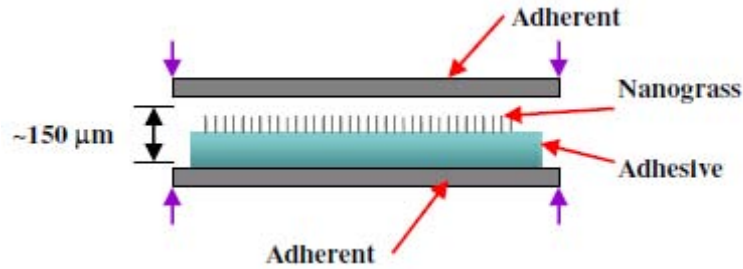


Figure 12. Nanograss-enhanced polymer adhesive joint for improved through-thickness thermal conductivity [59].

harvesting/storage and structural health monitoring. Several recent review articles have already covered much of the recent research related to sensors and actuators that can be used in multifunctional structures. For example, Li, et al. [6] and Gibson, et al. [7] have reviewed recent research related to sensors and actuators based on carbon nanotubes and their composites. A review article by Ratna and Karger-Kocsis [18] covers recent research on shape memory polymers which have potential applications as sensors and/or actuators. Piezoelectric materials such as lead zirconate titanate (PZT), polyvinylidene fluoride (PVDF) and aluminum nitride (AlN) can be embedded in structures for sensing and actuation, as they naturally possess the required electromechanical coupling. The effectiveness with which a piezoelectric material converts applied mechanical energy to electrical energy (i.e., for sensing or energy harvesting) is characterized by the piezoelectric coupling coefficient [60]

$$k_s = \sqrt{\frac{U_E}{W_m}} \quad (2)$$

and the corresponding piezoelectric coupling coefficient for conversion of electrical energy to mechanical energy (i.e., for actuation) is

$$k_a = \sqrt{\frac{W_m}{U_E}} \quad (3)$$

The most widely used forms of piezoelectric materials are wafers [61] and thin films [62], and numerous publications have dealt with them over many years. Piezoelectric microelectromechanical systems (MEMS) for sensing and actuation have been the subject of

extensive research, and the state-of-the-art in this area has been very recently reviewed by Tadigadapa and Mateti [63]. So in order to avoid duplication, we focus here on other important recent developments in structurally integrated sensing and actuation in load-bearing multifunctional composite structures.

Although not as common as piezoelectric wafers or thin films, piezoelectric fibers have been investigated as possible active components of multifunctional fiber-reinforced composites. The earliest reports of piezoelectric fiber composites (PFC) were apparently published by Hagood and Bent [64] and Bent, et al. [65], who embedded micron sized piezoelectric fibers in an epoxy matrix to which PZT powder had been added to reduce the fiber/matrix dielectric mismatch. The PFC laminate was built up from PFC laminae embedded between conventional graphite/epoxy laminae and interlaminar electrodes which applied the electric field required for actuation. Good agreement was obtained between measured electrically-induced deformations and those predicted by a modified Classical Lamination Theory which included actuator-induced stress terms [65]. More recently developed hollow piezoelectric fibers [66, 67] offer the advantage of lower operating voltage and a broader choice of possible matrix materials compared with solid cross-section piezoelectric fibers. Brei and Cannon [67] investigated the hollow piezoelectric fiber concept in Fig. 13, with emphasis on the effects of three key design parameters (matrix/fiber Young's modulus ratio, aspect ratio of the individual fibers, and overall active composite volume fraction) on the performance, manufacturing and reliability of the active composites.

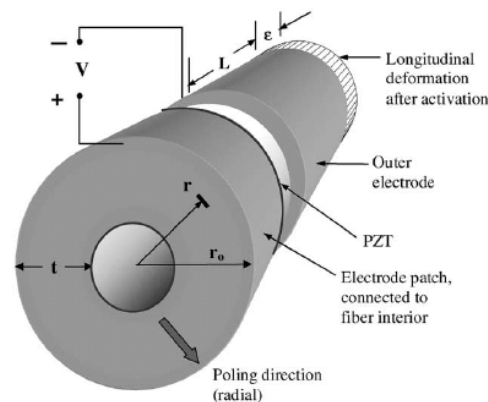


Figure 13. Hollow piezoelectric fiber with radial poling and longitudinal actuation of the fiber [67].

In Fig. 13, in the actuation mode, radial poling of the piezoelectric fiber results in longitudinal deformation of the fiber, while in the sensing mode, longitudinal deformation results in radial electrical output. Still more recently, Lin and Sodano [68, 69] developed piezoelectric structural fibers consisting of conductive structural fibers such as carbon coated with a piezoelectric interphase layer and an outer electrode layer (Fig. 14).

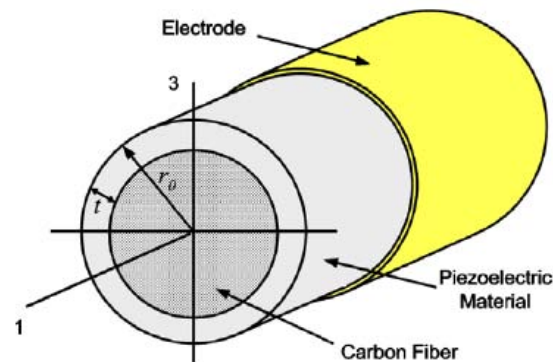


Figure 14. Multifunctional piezoelectric structural fiber [68].

As with the hollow piezoelectric fiber in Fig. 13, radial poling results in longitudinal actuation of the fiber and so forth. Finite element models of piezoelectric structural fiber/polymer matrix composites such as the one in Fig. 15 showed that the electromechanical coupling coefficients

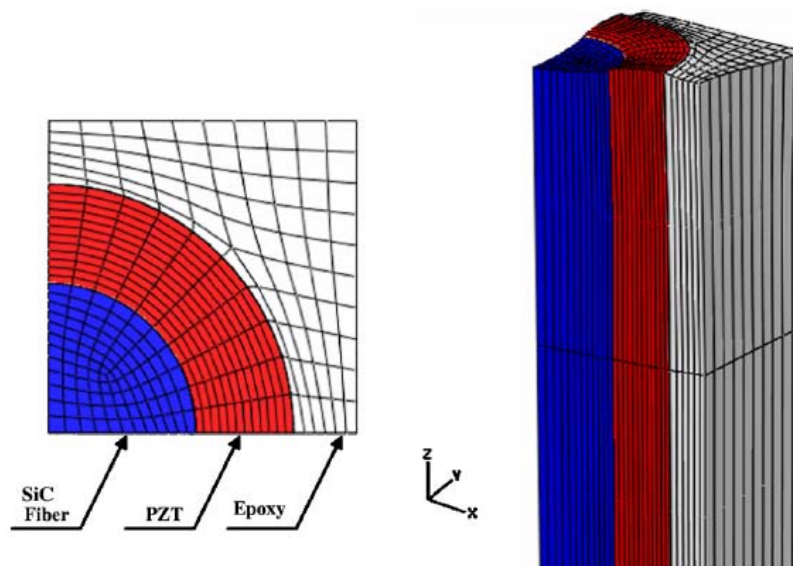


Figure 15. Finite element model of piezoelectric structural fiber embedded in a polymer matrix [68].

available from such composites can be as high as 65-70% of the corresponding coupling coefficient for the fiber itself, and that piezoelectric structural fiber composites are suitable for vibration control, damping, energy harvesting or structural health monitoring.

The capability of simultaneous control of stiffness and damping is a significant advantage of a new class of materials known as magnetorheological elastomers (MRE), which consist of conventional elastomers filled with micron-sized magnetizable particles such as iron. As reported by Fuchs, et al. [70], an applied magnetic field of variable strength was used to continuously and rapidly control stiffness and damping of a polybutadiene elastomer filled with 3-7 μm diameter carbonyl iron particles. In this case, the optimum concentration of the iron particles for greatest improvement of damping and stiffness was found to be 60 wt%, and other important variables which govern the stiffness and damping of MREs are the alignment of the magnetic particles and the temperature.

As indicated earlier, several recent review articles have dealt with the general area of structural health monitoring [11-14]. Here we will focus specifically on the use of embedded piezoelectric sensor/actuator networks for damage detection in composite structures due to its importance in the development of multifunctional structures. Lin and Chang [71] described the fabrication and initial validation testing of the Stanford Multi-Actuator-Receiver-Transduction (SMART) Layer® concept (Fig. 16).

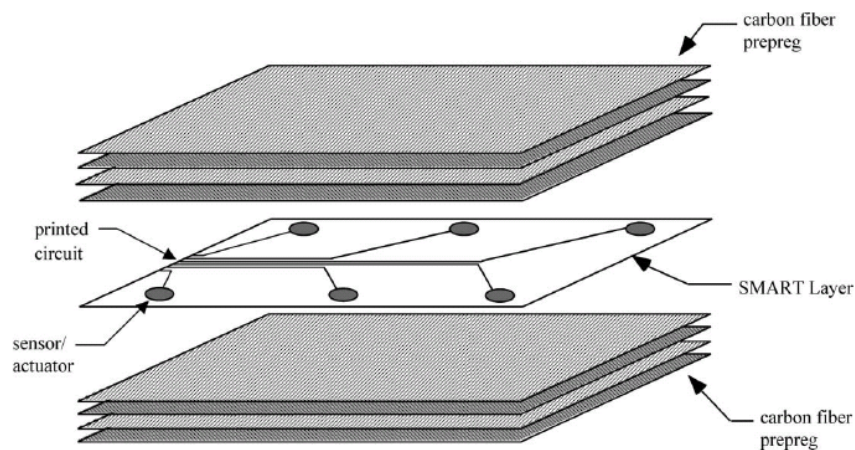


Figure 16. Stanford-Multi-Actuator-Receiver-Transduction (SMART) layer concept of integrated sensor/actuator network in a composite laminate[71].

This concept involves the use of printed circuit technology to produce a thin flexible, dielectric film with an array of networked piezoceramic actuators/sensors, which is embedded within a conventional composite laminate. It was shown that a conventional autoclave process and cure cycle can be used to fabricate carbon/epoxy composite laminates containing the SMART Layer®, that the layer does not significantly degrade the mechanical behavior of the composite, and that by measuring the phase delay between the transmitted and received stress wave during the cure process, the state of cure can be monitored. Subsequent research [72] showed that such layers can be integrated into composite structures fabricated by RTM and filament winding processes, and that the concept can be applied to either active or passive sensing to monitor the health of the structure throughout its lifetime. Still more recently, Wu, et al. [73] demonstrated the feasibility of an improved actuator/sensor network for damage detection in composite laminates based on the use of PZT actuators and fiber Bragg grating (FBG) fiber optic sensors instead of using PZTs for both actuating and sensing. The advantage of this approach lies in the decoupling of the signal transmission mechanisms and elimination of the signal crosstalk between actuator and sensor signals in the PZT actuator/sensor network. Other approaches to active sensor networks for damage detection in composite structures have been reported by Su, et al. [74,75]. Reports on the use of artificial neural networks to analyze the data from the piezoelectric sensor networks and classify and locate the damage in composite structures have been published by Watkins, et al. [76], Haywood, et al. [77], and Yu, et al. [78]. Similar systems have been adapted for control of smart laminated structures by Srivastava, et al. [79].

Layer-by-layer (LbL) assembly, which involves sequential deposition of dissimilar thin films at the nanoscale, has made it possible to develop sensors that are capable of detecting multiple phenomena. For example, Loh, et al. [80] used the LbL method to fabricate a carbon nanotube-polyelectrolyte multilayer composite material for monitoring strain and corrosion. In this case, the concentration of carbon nanotubes determines the sensitivity to strain and the type of polyelectrolyte determines the sensitivity to pH. Deposition of such a LbL sensor on a miniature planar coil antenna results in a passive wireless sensor which does not require a battery power supply [81]. The LbL method can also be used to fabricate high strength multifunctional composites for biological implants, anticorrosion coatings, and thermal/electrical interface materials [82, 83]. Shape memory polymers also have great potential for use in sensors and

actuators. This is particularly true for electroactive shape memory polymer composites containing conductive fillers [18].

3.3 Energy harvesting/storage

The basic idea behind energy harvesting/storage as related to multifunctional structures is to parasitically extract energy from the motion and/or deformation of a host structure and convert it to electrical energy which can be stored and used for other purposes. One popular application is to power small electronic devices such as wireless sensors for structural health monitoring. Several review articles have already been published on this subject [14-17], and since the discussion of sensors and actuators in the previous section is also highly relevant to energy harvesting, the emphasis in this section will be on recent developments in energy storage in load-bearing multifunctional structures.

The most common mode of energy harvesting involves the use of piezoelectric materials to convert mechanical deformations from vibrating structures such as beams and plates to electrical energy. It appears that Sodano, et al. [84] were the first to report that the power output from a randomly vibrating piezoelectric material is capable of recharging a discharged nickel metal hydride battery. They also reported on the use of the piezoelectric output to charge a capacitor, but concluded that the capacitor discharge occurred too quickly for practical energy storage and that batteries provided more flexibility in use of the stored energy.

In a multifunctional structure, the battery should become part of the load-bearing structure. Pereira, et al. [85,86] embedded thin film lithium energy cells within carbon/epoxy laminates to form energy storage structural composites. The lithium energy cells did not significantly change the strength and stiffness of the carbon/epoxy laminate, and the energy cells charged and discharged normally when the composite was mechanically loaded to as high as 50% of its ultimate tensile strength. Further integration was achieved by Kim, et al. [87], who used a copper nano-inkjet-printed circuit on a polymer film to interconnect a thin-film solar module and a thin-film lithium-ion battery. The resulting film was embedded and co-cured within carbon/epoxy prepreg layers to fabricate an energy harvesting/storage laminate. The multifunctional laminate

was then subjected to mechanical loading. As shown in Figure 17, when the ink-jet-printed electrodes are thicker than 4 μm , they did not exhibit any significant resistance change up to the maximum strain of 1%.

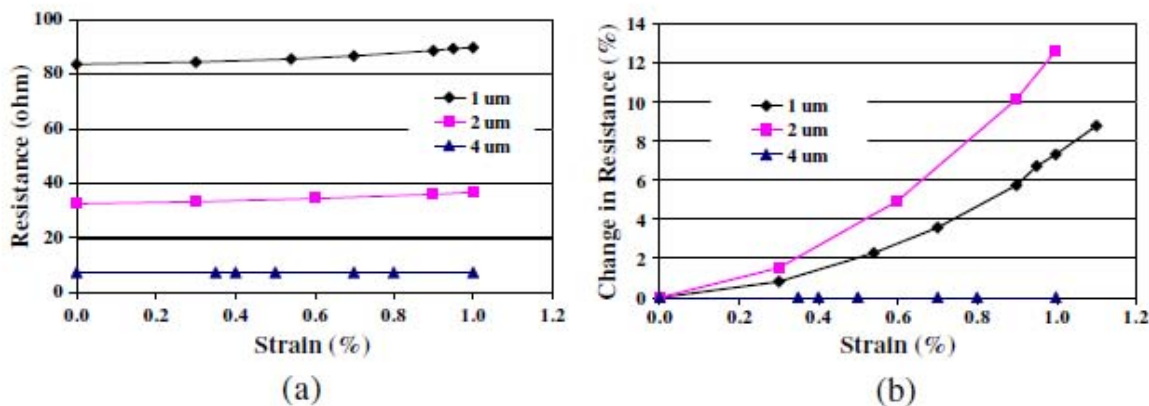


Figure 17. Resistance of inkjet-printed 160 μm -wide electrode under static loading for several electrode thicknesses: (a) resistance; (b) percentage of resistance change [87].

Liu, et al. [88] developed a new load/bearing structural battery in which the polymer cathode in a conventional polymer lithium-ion battery (Fig. 18) was replaced by a higher molecular weight, carbon nanofiber-reinforced polymer (Fig. 19), the organic liquid electrolyte was replaced with a solid-state polymer electrolyte and the separator region was reinforced with non-conducting fibers.

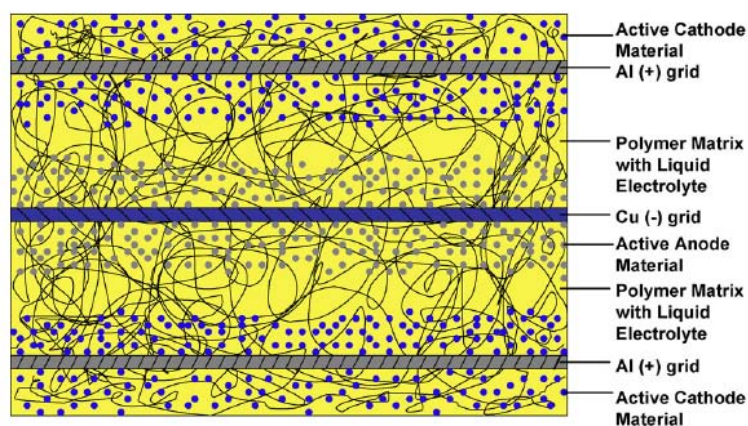


Figure 18. Construction of conventional nonstructural polymer lithium-ion battery [88].

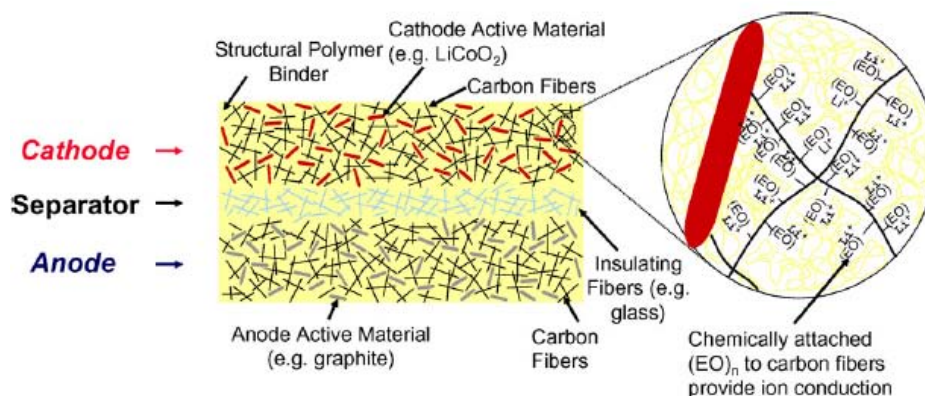


Figure 19. Construction of new structural battery [88].

Although this design represents a starting point, the tensile modulus of the battery was only about 3 GPa, and the energy density was low compared with that of a conventional lithium-ion battery, so further work is needed to develop a usable structural battery. Snyder, et al. [89] investigated different polymer electrolyte formulations for multifunctional structural batteries ranging from highly conductive and structurally weak to poorly conductive and highly structural. As shown in Fig. 20, it was found that the electrical conductivity and the elastic modulus of the different formulations are inversely related, which makes it difficult to optimize both properties.

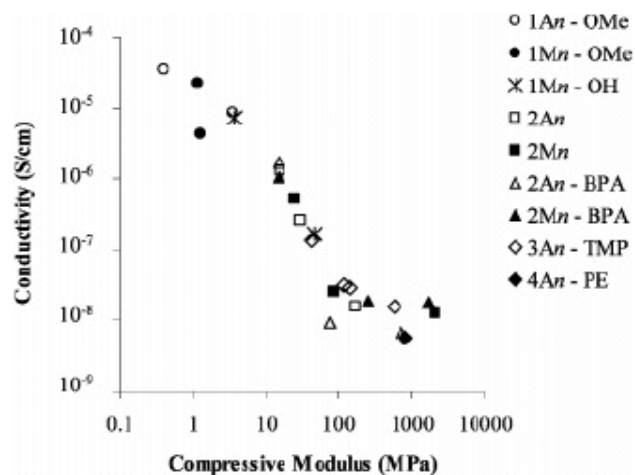


Figure 20. Experimental data showing inverse relationship between electrical conductivity and compressive modulus for several polymer electrolytes for use in structural batteries [89].

In a separate paper, Snyder, et al. [90] investigated the properties of commercial carbon fabric materials, carbon nanotube papers and nanofoam papers for possible use as anodes in multifunctional lithium-ion batteries. IM-7 and T300 PAN-based carbon fabrics yielded the best balance between electrochemical and tensile strength performance, whereas the pitch-based fabrics exhibited poor multifunctional performance. The nanofoam papers had the best electrochemical performance but the mechanical properties were poor.

Although structural integrated batteries are more practical for slower discharge over a longer period of time, structurally integrated capacitors can provide energy storage for quick discharge at high energy levels. O'Brien, et al. [91] compared stiffness and energy density of various structural capacitors. As shown in Fig. 21, conventional capacitors have high energy density but poor stiffness, whereas structural composites have good stiffness but poor energy density.

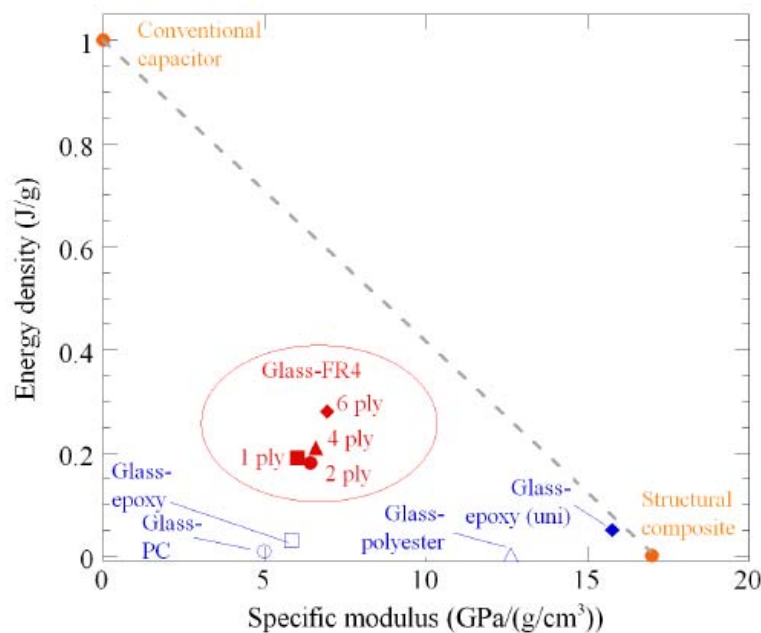


Figure 21. Energy density and specific modulus of multifunctional structural capacitors. Dashed line represents design goal for true multifunctionality [91].

None of the materials evaluated met the design goal of multifunctional efficiency for system level weight savings shown by the dashed line in Fig. 21. In a continuation of this work, Baechle, et al. [92] addressed design issues for improving multifunctional efficiency and scaling issues related to manufacturing. Luo and Chung [93] developed a high capacitance structural capacitor consisting of a carbon/epoxy laminate with a paper interlayer to reduce through-the-thickness conductivity, but the capacitor was not mechanically tested. Lin and Sodano [94] demonstrated that their previously developed SiC/BaTiO₃ piezoelectric structural fiber [69] could be used as a structural capacitor by taking advantage of the dielectric nature of the BaTiO₃ coating on the SiC fiber (i.e., the BaTiO₃ coating was employed as a cylindrical capacitor). Fibers with an aspect ratio of 0.23 were found to be the best for energy storage.

3.4 Self-healing capability

A truly autonomous multifunctional structure will be capable of healing itself when damaged, as a biological system would, and recent research has demonstrated the feasibility of such materials, particularly polymeric materials. A comprehensive review of publications in the area of self-healing polymeric materials has recently appeared [13], so only a few representative publications will be discussed here. White, et al. [95] developed self-healing polymers and polymer composites based on the use of a microencapsulated healing agent and a catalyst for polymerizing the healing agent. As shown in Figure 22, when damage causes cracks in the

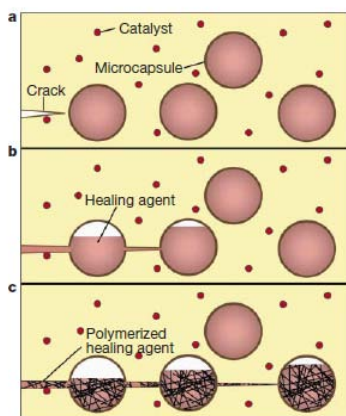


Figure 22. Illustration of self-healing of cracks in polymers by the use of a microencapsulated healing agent and a catalyst for polymerizing the healing agent [96].

polymer, the cracks break open the microcapsules, causing the healing agent to leak into the crack by capillary action. The healing agent then reacts with the catalyst, causing polymerization that bonds the crack faces together. Mode I fracture toughness tests of virgin epoxy and self-healed epoxy specimens using the tapered double cantilever beam (TDCB) test in Fig. 23(a) showed that fracture load and corresponding fracture toughness for the self-healed specimens reached up to 75% of the corresponding values for the virgin uncracked specimens.

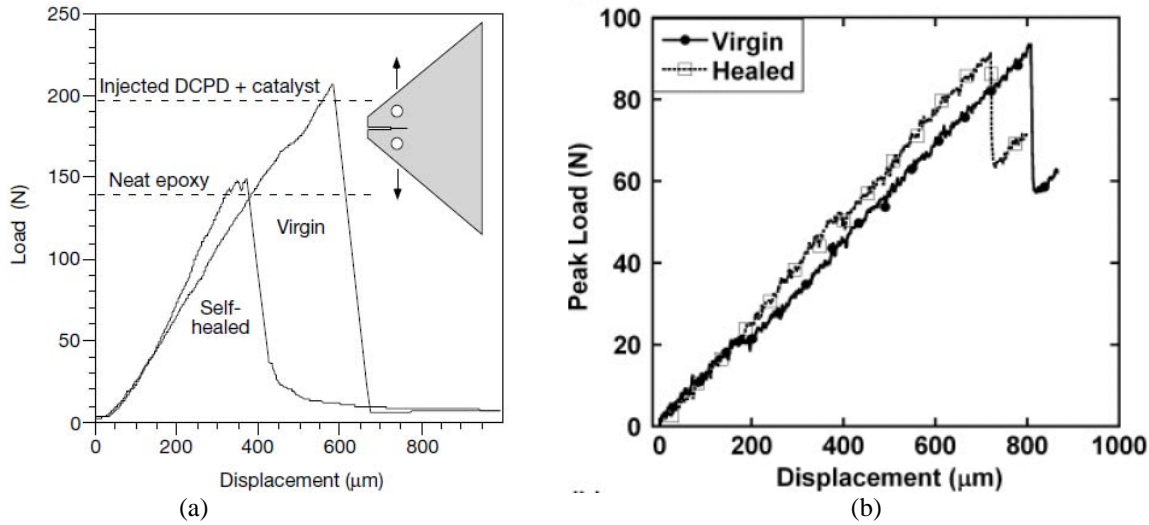


Figure 23. Load-displacement curves for Mode I fracture toughness tests of virgin and self-healed specimens (a) microcapsules contain solvent healing agent only [95], and (b) microcapsules contain a mixture of epoxy monomer and solvent [97].

The crack healing efficiency for the fracture toughness test is defined as

$$\eta = \frac{K_{Ic_{healed}}}{K_{Ic_{virgin}}} = \frac{P_{c_{healed}}}{P_{c_{virgin}}} \quad (4)$$

Further research on optimization of the microcapsule concentration and choice of catalyst led to crack healing efficiencies of over 90% ($\eta = 0.9$) in self-healed specimens and maximum healing efficiency was achieved within 10 hours of the fracture event [96]. Still more recently, Caruso, et al. [97] obtained complete recovery of virgin fracture toughness ($\eta = 1$) by replacing the original solvent healing agent in the microcapsules with epoxy-solvent microcapsules containing a mixture of epoxy monomer and solvent. As shown in Fig. 23(b), the resulting load-

displacement curves indicate full recovery of virgin fracture toughness. Related research by the same group has considered self-healing polymers under fatigue loading [98-100] and low-velocity impact loading [101], as well as the development of self-healing polymer coatings to provide effective corrosion protection for steel substrates [102], and the use of three-dimensional microvascular networks in the substrate beneath an epoxy coating to enable continuous delivery of healing agents for self-healing of repeated crack damage in the coating [103].

Other recent developments in self-healing polymer composites include the use of different methods of healing agent microencapsulation such as nanoporous silica capsules [104] and nanoporous glass fibers [105]. The use of self-healing polymers as the matrix material in carbon fiber reinforced composites has also been considered by Williams, et al. [106]. Yin, et al. [107] found that the self-healing ability of woven glass fabric/epoxy composites containing healant microcapsules degraded with storage time. The likely cause is believed to be time-dependent diffusion of the epoxy monomer from the microcapsules following contraction of the microcapsules during the cure process. This degradation was found to be a self-limiting process as the leaked epoxy gradually cured and blocked the diffusion sites on the microcapsules, but it was concluded that further research is needed to improve the microcapsule designs and materials.

Most of the research on self-healing materials has been based on experimental work, and only a few publications have dealt with analytical modeling of the self-healing process. Balazs [108] has briefly reviewed computational models for self-healing materials, while pointing out that the area is still in its infancy and that solutions will require the development of multidisciplinary methods involving models for fluid dynamics, structural mechanics, chemical reactivity, and phase transitions. Barbero, et al. [109] have applied the principles of continuum damage mechanics to the case of self-healing composites, while Maiti, et al. [110] and Geubelle and Maiti [111] employed an artificial crack closure approach involving cohesive modeling and a contact algorithm. Park, et al. [112] used a conventional cure kinetics model and electrical resistance heating of the polymer matrix above the glass transition temperature to achieve self-healing of a carbon fiber /epoxy composite.

3.5 Electromagnetic interference (EMI) shielding

Electromagnetic interference (EMI) occurs when an undesirable disturbance due to electromagnetic conduction or radiation from an external source interferes with the operation of an electrical circuit. The usual solution to EMI is to protect the circuit with an EMI shielding material or structure, and the shielding effectiveness, SE, is defined in decibels (dB) as

$$SE = 20 \log \frac{E_t}{E_i} = 20 \log \frac{H_t}{H_i} \quad (5)$$

Electrically conducting metallic materials have excellent SE, but due to reduced weight and other desirable properties, nonmetallic materials such as polymers and polymer composites are increasingly used to replace metals. SE is particularly important for multifunctional materials and structures which are typically based on polymer composites, and where both electrical and mechanical functions are typically involved. In order to achieve acceptable SE, the polymer must be either an intrinsically conducting polymer (ICP) or be filled with a conducting material such as carbon fibers or nanotubes or be coated with a conductive coating. Several recent review articles have discussed various aspects of EMI shielding, especially for polymers. Chung [113] reviewed publications on materials for EMI, Geetha, et al. [114] surveyed recent research on methods and materials for EMI, while Wang and Jing [115] reviewed articles dealing with ICPs for EMI.

While ICPs such as polyaniline (PANI) and polypyrrole (PPY) are very effective for EMI shielding, their mechanical effectiveness when used as matrix materials in multifunctional fiber composite structures is not clear. However, blends of ICPs such as PANI with established structural polymers like epoxy resins may be a more practical approach. Jia, et al. [116] studied electrical conductivity of PANI/epoxy composites having different PANI morphologies. As shown in Fig. 24, the composites containing PANI wires had a lower percolation threshold than the composites containing PANI particles or PANI fibers. This is because the PANI wires have the highest aspect ratio and are able to more easily form continuous conductive networks within the nonconducting epoxy. As indicated in Section 3.1, the use of other high aspect ratio

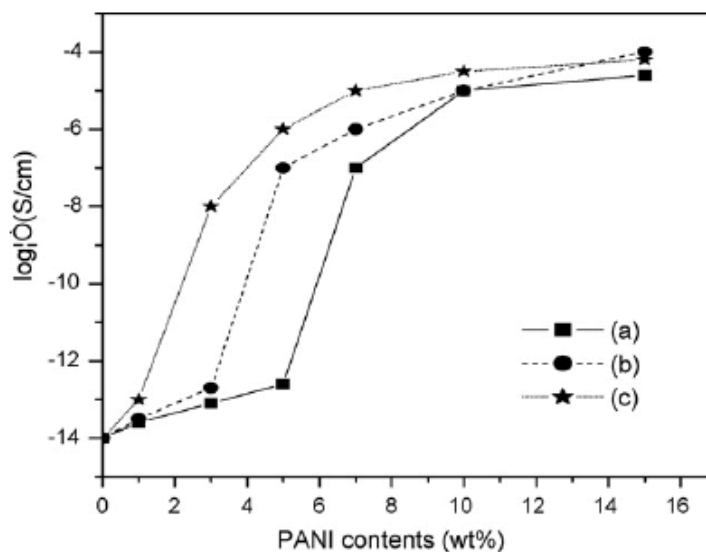


Figure 24. Electrical conductivity for PANI/epoxy composites at different PANI contents and different PANI morphologies (a) PANI particles, (b) PANI fibers, and (c) PANI wires [116].

electrically conducting nanofillers in polymers is also an effective means of creating electrically conducting polymer composites, which in turn should be suitable for EMI shielding. For example, Huang, et al. [117] and Al-Saleh and Sundararaj [118] have investigated the EMI shielding characteristics of carbon nanotube/polymer composites, while the EMI shielding properties of carbon nanofiber/polymer composites have been studied by Yang, et al. [119]. A review of recent articles on conductivity and EMI shielding characteristics of vapor grown carbon nanofiber/polymer composites has been published by Al-Saleh and Sundararaj [120].

Most of the publications listed so far involve experimental work, and there is a need for development of more analytical models to compliment the experiments. Analytical models are needed not only to help in interpreting the experimental results, but in optimizing the multifunctional material or system for specific applications.

4. Recent applications of multifunctional materials and structures

Much of the research on multifunctional materials and structures has been driven by current and potential aerospace applications. For example, motivated primarily by potential aircraft applications and by technological advances in composite materials, sensing, actuation and

controls, the ability of a multifunctional structure to reconfigure, or morph itself as its operating environment and/or its mission profile changes has been a subject of great research interest in recent years. One major goal of such research is to develop multifunctional aircraft wings which can change shape in different phases of flight as a bird wing does. A major application of these technologies is for morphing aircraft skins, and a comprehensive review of publications on morphing skins has been published recently by Thill, et al. [121]. Since the publication of this review article, several relevant applications-oriented publications have appeared. For example, Wildschek and Plotner reported on the development of an all-composite, all-electric morphing trailing edge for flight control on a blended wing body airliner [122], Hartl, et al. [123,124] described the use of a shape memory alloy for active jet engine chevron applications, and Mudupu, et al. [125] discussed the design and validation of a fuzzy logic controller and a piezoelectric composite actuator for a smart projectile fin.

Structurally integrated batteries for energy storage are another recent application of multifunctional structure design. The effectiveness of a multifunctional system is best defined by using a metric that characterizes the particular system, such as flight endurance time for an aircraft vehicle. For example, as reported by Thomas and Qidwai [126,127] structurally integrated batteries can extend the flight endurance time of an electrically-propelled unmanned air vehicle (UAV). The flight endurance time of the UAV is given by [126,127]

$$t_E = \left(\frac{E_B \eta_B}{(W_S + W_B + W_{PR} + W_{PL})^{3/2}} \right) \left[\frac{\rho S C_L^2}{2 C_D^2} \right]^{1/2} \eta_P \quad (6)$$

This equation shows that integrating the battery with the structure or one of the other subsystems can lead to an increased flight endurance time, t_E . Further analysis of this equation for change in t_E with changes in battery and structure weight shows that decreasing the weight is 1.5 times more effective in increasing t_E than is increasing the battery energy [126]. By integrating a polymer lithium-ion battery in the carbon/epoxy composite wing skin structure of the DARPA Wasp micro air vehicle (MAV), a record-setting flight endurance time for the vehicle was achieved [127]. A photo of this vehicle is shown in Fig. 25.



Figure 25. First generation DARPA Wasp micro air vehicle with polymer lithium-ion battery (silver quadrilaterals) integrated in composite wing skin structure [127].

Another example of multifunctional structure technology that is driven by aerospace applications is the integration of an electronic communications antenna into the load-bearing composite structure of an aircraft. The conformal load bearing antenna structure (CLAS) development effort sponsored by the U. S. Air Force's Smart Skin Structure Technology Demonstration (S³TD) program intends to develop the technology to embed a broad band RF antenna into the composite skin of a fighter aircraft [128-131]. More recent research related to the CLAS has involved the design and fabrication of a microstrip antenna which is integrated in a three dimensional orthogonal woven composite structure [132], impact testing of these structures [133], and wireless detection of damage in composite structures by making use of the composite structure itself as an antenna/sensor system [134].

Composite sandwich structures present some interesting possibilities for multifunctional applications. For example, Wirtz, et al. [135] have described the thermal and mechanical behavior of a multifunctional thermal energy storage sandwich structure for use in the temperature control system of an electronics module. The multifunctional structure has a thermal interface connected to a hollow aluminum plate which has a series of small compartments that are filled with phase change material. Heat storage is via the latent heat of the phase change material. The thermal energy storage and mechanical behavior of the structure are characterized and it is determined that the structure has an excellent performance-to-weight ratio. Queheillalt,

et al. [136] developed a multifunctional heat pipe sandwich structure which integrates the thermal management capabilities of a heat pipe with structural load support. Ozaki, et al. [137] reported on multifunctional sandwich panels for space satellites, in which electronic modules are embedded between the face sheets of carbon fiber composite/honeycomb core sandwich panel. The mechanical, electrical and thermal characteristics of the panel were evaluated, and significant reductions in weight, cost and production time were achieved. The use of a carbon foam core and carbon fiber composite face sheets to enhance both through-the-thickness and in-plane thermal conductivities of sandwich panels for lightweight spacecraft thermal radiators has been described by Silverman [138]. In the automotive industry, there is great interest in multifunctional structures in which static, dynamic and acoustic behaviors are optimized. Rather than taking the traditional approach of treating the design, manufacture and assembly of the automobile body structure, acoustic treatments and interior trim separately, Cameron, et al. [139] have used finite element models to study a multifunctional approach in which an integrated, multi-layered sandwich is used to replace a traditional roof panel with its separate components. Vaidya, et al. [140] developed a multifunctional sandwich structure in which the woven E-glass face sheets are connected with vertical woven E-glass piles and the foam core. This construction enhances the impact resistance and sound/vibration damping and accommodates wires or sensors. Sandwich structures often consist of composite face sheets and foam cores, and there is increased activity in the use of nanoparticles to enhance both the manufacturing process and the mechanical properties of foams. The manufacturing process for foams is enhanced because the nanoparticles serve as nucleation sites for bubbles during the foaming process, leading to increased density and reduced cell size. Mechanical properties of the foams are also enhanced due to the reinforcement effect of the nanoparticles. Lee, et al. [141] have reviewed the literature in the area of polymer nanocomposite foams.

Among the most challenging and promising applications of multifunctional materials and structures are those in the biomedical field, and much of the recent activity in this area has been driven by advances in nanomaterials and nanostructures. For example, multifunctional nanoparticles have great potential for drug/antibody delivery in combination with diagnostics and therapeutics. Since 2000 there has been a surge in the number of journal articles related to multifunctional nanoparticles, as shown clearly in Figure 26. Suh, et al. [142] have reviewed the

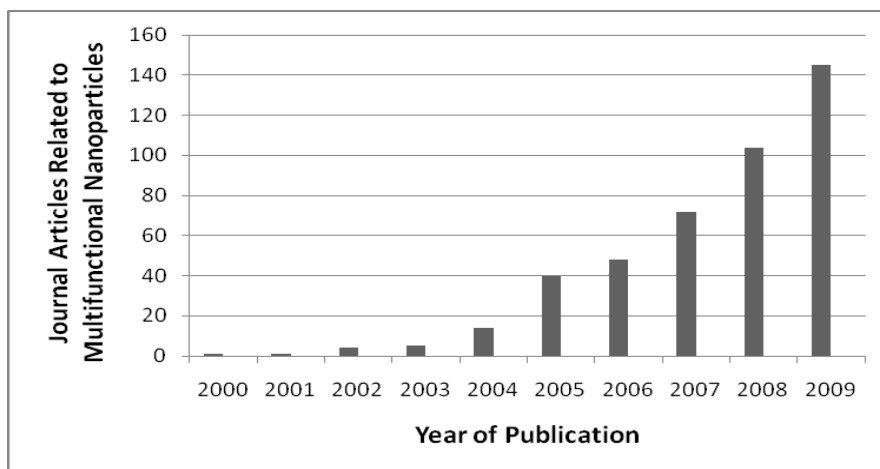


Figure 26. Recent English language refereed journal articles related to multifunctional nanoparticles. Data collected from Engineering Village© web-based information service.

developments in multifunctional nanoparticle systems (MFNPS) for biomedical applications, and Figure 27 illustrates one possible configuration of such a MFNPS. The matrix of the MFNPS could be a metal oxide network which hosts sub-domain inclusions such as fluorescent optical probes, magnetically susceptible particles for magnetic resonance imaging, and pores or functionalities which can host small bioactive molecules such as drugs or antibodies. Inclusions can be either organic, inorganic or hybrid organic/inorganic [142].

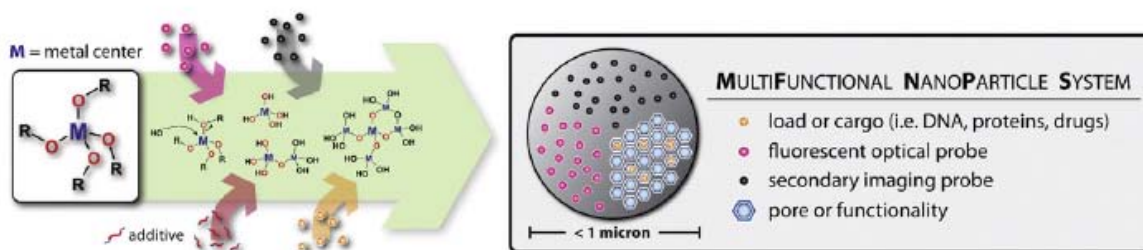


Figure 27. Illustration of multifunctional nanoparticle (MFNPS) system for biomedical applications [142].

A bionanoengineering design process for multilayered MFNPS is described by Haglund, et al. [143], and such a multilayered particle is illustrated in Figure 28. MFNPS offer great hope for early detection of cancer and delivery of therapeutic drugs for cancer treatment. Publications related to the development of MFNPS for cancer imaging and therapy have been reviewed by

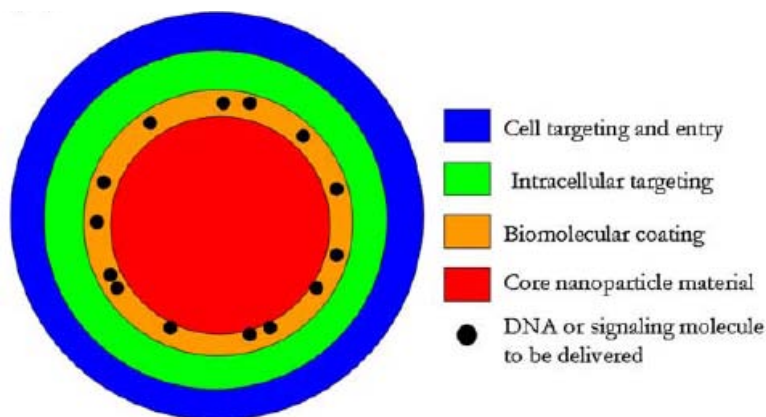


Figure 28. Illustration of multilayered MFNPS [143].

Park, et al. [144]. MFNPS which have a combination of magnetic and fluorescent properties are of great interest for in vitro imaging techniques such as MRI, as well as for therapy and for external magnetic manipulation in building biomedical nanodevices. Corr, et al.[145] have reviewed recent publications in multifunctional magnetic-fluorescent nanocomposites for biomedical applications. The surface area-to-volume ratio, A/V , for a spherical particle is inversely proportional to its radius, so A/V for a nanometer-sized particle will be 1000 times greater than A/V for a micron-sized particle. The large A/V ratios and resulting large pore volumes for porous hollow nanostructures make them particularly attractive for multifunctional delivery of drugs and biomolecules. Recent publications on the synthesis and applications of hollow micro/nanostructures have been reviewed by Lou, et al. [146], while biomedical applications of hollow nanostructures have been reviewed by An and Hyeon [147].

A number of biomedical applications for multifunctional materials require substantial flexibility in order to accommodate large deformations. For example, artificial muscles must be flexible and strong enough to be capable of sensing and actuation over large ranges of deformation. Biomedical applications include peristaltic pumps, robot arms, artificial hands and grippers. One such class of materials that has been the subject of considerable research are the ionic polymer-metal composites (IPMC), which are excited by an electric field. Shahinpoor and Kim have published a series of four review articles dealing with the fundamentals [148], manufacturing techniques [149], modeling and simulation [150], and industrial and biomedical applications

[151] of IPMCs. Electroactive polymers with high dielectric constants can also generate large deformations under an electric field, as reviewed by Bar-Cohen. [152]. As another example, energy harvesting from normal motions and deformations of the human body requires that the energy conversion device be very flexible. Qi, et al. [153] have developed a flexible energy conversion device based on printing of piezoelectric PZT ribbons with micrometer-scale widths and nanometer scale thicknesses on rubber substrates. The use of carbon nanotubes in flexible electronic yarns and fabrics for use in wearable biomonitoring and telemedicine sensors has been reported by Shim, et al. [154]. An energy harvesting backpack for use by soldiers was developed by Granstrom, et al. [155] who replaced the nylon shoulder straps on a standard backpack with flexible PVDF piezoelectric straps. During normal walking motions, the relative motions between the soldier's body and the backpack generate deformations in the PZT straps, which then convert these deformations to electrical energy for use in powering small portable electronic devices carried by the soldier.

Multifunctionality in impact resistant materials for military transport vehicles, helicopters and fighter aircraft is becoming increasingly important, and one example is optically transparent, impact-resistant nanocomposite materials for windows in such vehicles. The extremely small size and small concentration of nanoreinforcements makes it possible to improve impact energy absorption while maintaining good transparency. Such materials have been investigated by Rai and Singh [156], who fabricated and tested sandwich panels consisting of PMMA sheets with thin layers of nano-enhanced polymer adhesive sandwiched between them. The polymer adhesive layers were enhanced with 2 wt% of 35 nm sized alumina powder. Drop weight impact tests were used to determine impact energy and optical transparency was measured using a spectrophotometer. Significant improvement in impact energy was achieved with the nano-enhanced adhesive layers, while transparency was somewhat reduced but acceptable. Related investigations of impact resistant, optically transparent composites have been reported by Liu, et al. [157], Rojanapitayakorn, et al. [158], Song, et al. [159], and Huang, et al. [160].

5. Concluding Remarks

This article attempts a reasonably comprehensive review of representative journal publications covering developments in mechanics of multifunctional materials and structures. Most of the

articles have appeared since 2000, and many involve polymer composites, nanomaterials and nanostructures. Functions of interest include structural properties like strength, stiffness, fracture toughness, and damping, and nonstructural functions like electrical and/or thermal conductivity, sensing and actuation, energy harvesting/storage, self-healing capability, and electromagnetic interference (EMI) shielding. Much of the future research on multifunctional materials and structures will be driven by not only structural applications like aircraft, but by needs in other areas like biomedical. There is a need for more analytical modeling work in most of the areas covered in this review, since most of the published results to date tend to be experimental in nature. Analytical models are needed not only to help in interpreting the experimental results, but in optimizing the multifunctional material or system for specific applications.

Acknowledgements

The author gratefully acknowledges the financial support from Award No. FA9550-09-1-0506 from the U.S. Air Force Office of Scientific Research, and the encouragement of Dr. Les Lee, Program Manager for the AFOSR Mechanics of Multifunctional Materials and Microsystems Program. The author is very grateful for the electronic access to the Engineering Village© web-based information service through the Mathewson-IGT Knowledge Center at the University of Nevada, Reno, without which this article would not have been possible.

References

1. Baur J, Silverman E. Challenges and opportunities in multifunctional nanocomposite structures for aerospace applications. *MRS Bulletin* 2007; 32(4): 328-334.
2. Ye L, Lu Y, Su Z, Meng G. Functionalized composite structures for new generation airframes: a review. *Compos Sci Technol* 2005; 65(9): 1436-1446.
3. Thostenson ET, Ren Z, Chou T-W. Advances in the science and technology of carbon nanotubes and their composites: a review. *Compos Sci Technol* 2001; 61: 1899-1912.
4. Chou T-W, Gao L, Thostenson ET, Zhang Z, Joon-Hyung B. An assessment of the science and technology of carbon nanotube composites. *Compos Sci Technol* 2009; Accepted manuscript, on line.
5. Breuer O, Sundararaj U. Big returns from small fibers: A review of polymer/carbon nanotube composites. *Polymer Compos* 2004; 25(6): 630-645.
6. Li C, Thostenson ET, Chou T-W. Sensors and actuators based on carbon nanotubes and their composites: A review. *Compos Sci Technol* 2008; 68: 1227-1249.
7. Gibson RF, Ayorinde EO, Wen Y-F. Vibrations of carbon nanotubes and their composites: a review. *Compos Sci Technol* 2007; 67: 1-28.
8. Sun L, Gibson RF, Gordaninejad F, Suhr J. Energy absorption capability of nanocomposites: a review. *Compos Sci Technol* 2009; 69: 2392-2409.
9. Bauhofer W, Kovacs JZ. A review and analysis of electrical percolation in carbon nanotube polymer composites. *Compos Sci Technol* 2009; 69(10): 1486-1498.
10. Birman V, Byrd LW. Modeling and analysis of functionally graded materials and structures. *Appl Mech Rev* 2007; 60(1-6): 195-216.

11. Montalvao D, Maia NMM, Ribeiro AMR. A review of vibration-based structural health monitoring with special emphasis on composite materials. *Shock Vib Digest* 2006; 38(4): 295-324.
12. Zou Y, Tong L, Steven GP. Vibration-based model dependent damage identification and health monitoring for composite structures – a review. *J Sound Vib* 2000; 230(2): 357-378.
13. Wu DY, Meure S, Solomon D. Self-healing polymeric materials: A review of recent developments. *Prog Polym Sci* 2008; 33(5): 479-522..
14. Park G, Rosing T, Todd MD, Farrar CR, Hodgkiss W. Energyharvesting for structural health monitoring sensor networks. *J Infrastruct Systems* 2008; 14(1): 64-79.
15. Sodano HA, Inman DJ, Park G. A review of power harvesting from vibration using piezoelectric materials. *Shock Vib Digest* 2004; 36(3): 197-205.
16. Anton SR, Sodano HA. A review of power harvesting using piezoelectric materials (2003-2006). *Smart Mater Struct* 2007; 16(3): R1-R21.
17. Cook-Chennault KA, Thambi N, Sastry AM. Powering MEMS portable devices – a review of non-regenerative and regenerative power supply systems with special emphasis on piezoelectric energy harvesting systems. *Smart Mater Struct* 2008; 17(4): 043001.
18. Ratna D, Karger-Kocsis J. Recent advances in shape memory polymers and composites: A review. *J Mater Sci* 2008; 43(1): 254-269.
19. Gibson R, Gianaris NJ, Lucht B, Beckwith SW, Editors. Proc 2008 SAMPE Fall Tech Conf “Multifunctional Materials: Working Smarter Together”, Sept. 8-11, 2008, Memphis, TN. Soc for Adv of Mater and Process Engr.
20. Lau K, Cheng L, Su Z, Varadan VK. Smart Composite Materials: Selected papers from the International Conference on Multifunctional Materials and Structures (MFMS 08), Hong Kong, 28-31 July 2008. *Smart Mater Struct* 2009; 18(7): 070201.
21. Gibson RF, Chen Y, Zhao H. Improvement of vibration damping capacity and fracture toughness in composite laminates by the use of polymeric interleaves. *J Engr Mater Technol* 2001; 123: 309-314.
22. Koratkar NA, Suhr J, Joshi A, Kane RS, Schadler LS, Ajayan PM, et al. Characterizing energy dissipation in single-walled carbon nanotube polycarbonate composites. *Appl Phys Lett* 2005;87: 063102.
23. Zhou X, Shin E, Wang KW, Bakis CE. Interfacial damping characteristics of carbon nanotube-based composites. *Compos Sci Technol* 2004;64:2425–37.
24. Rajoria H, Jalili N. Passive vibration damping enhancement using carbon nanotube-epoxy reinforced composites. *Compos Sci Technol* 2005;65:2079–93.
25. Koratkar NA, Wei BQ, Ajayan PM. Carbon nanotube films for damping applications. *Adv Mater* 2002;14(13–14):997–1000.
26. Koratkar NA, Wei BQ, Ajayan PM. Multifunctional structural reinforcement featuring carbon nanotube films. *Compos Sci Technol* 2003;63(11):1525–31.
27. Teh PL, Mariatti M, Akil HM, Yeoh CK, Seetharama KN, Wagiman ANR, Beh KS. The properties of epoxy resin coated silica fillers composites. *Mater Letters* 2007; 61: 2156-2158.
28. Manjunatha CM, Taylor AC, Kinloch AJ, Sprenger S. The tensile fatigue behavior of a GFRP composite with rubber particle modified epoxy matrix. *J Reinf Plastics Compos OnlineFirst*, September 8, 2009, doi:10.1177/0731684409344652.
29. Vlasveld DPN, Bersee HEN, Picken SJ. Nanocomposite matrix for increased fibre composite strength. *Polymer* 2005; 46: 10269-10278.
30. Zhao Z-G, Ci L-J, Cheng H-M, Bai, J-B. The growth of multiwalled carbon nanotubes with different morphologies on carbon fibers. *Carbon* 2005; 43: 651-673.
31. Uddin MF, Sun CT. Strength of unidirectional glass/spoxy composite with silica nanoparticle-enhanced matrix. *Compos Sci Technol* 2008; 68(7-8): 1637-1643.
32. Uddin MF, Sun CT. Improved dispersion and mechanical properties of hybrid nanocomposites. *Compos Sci Technol* 2010; 70: 223-230.
33. Liu S, Zhang H, Zhang Z, Zhang T, Sprenger S. Tailoring the mechanical properties of epoxy resin by various nanoparticles. *Polymers & Polymer Compos* 2008; 16(8): 471-477.
34. Zhang H, Tang L-C, Zhang Z, Friedrich K, Sprenger S. Fracture behavior of in situ nanoparticle-filled epoxy at different temperatures. *Polymer* 2008; 49: 3816-3825.

35. Manjunatha CM, Taylor AC, Kinloch AJ. The effect of rubber micro-particles and silica nano-particles on the tensile fatigue behavior of a glass fibre epoxy composite. *J Mater Sci* 2009; 44: 342-345.
36. Cho J, Joshi MS, Sun CT. Effect of inclusion size on mechanical properties of polymeric composites with micro and nano particles. *Compos Sci Technol* 2006; 66: 1941-1952.
37. Cho J, Sun CT. A molecular dynamics simulation study of inclusion size effect on polymeric matrix composites. *Comput Mater Sci* 2007; 41: 54-62.
38. Thostenson ET, Li WZ, Wang DZ, Ren ZF, Chou T-W. Carbon nanotube/carbon fiber hybrid multiscale composite. *J Appl Phys* 2002; 91(9): 6034-6037.
39. Veedu VP, Cao A, Li X, Ma K, Soldano C, Kar S, Ajayan PM, Ghasemi-Nejhad MN. Multifunctional composites using reinforced laminae with carbon nanotube forests. *Nature Mater* 2006; 5: 457-462.
40. Garcia EJ, Hart AJ, Wardle BL. Long carbon nanotubes grown on the surface of fibers for hybrid composites. *AIAA J* 2008; 46(6): 1405-1412.
41. Garcia EJ, Wardle BL, Hart AJ. Joining prepreg composite interfaces with aligned carbon nanotubes. *Compos Part A: Appl Sci & Manuf* 2008; 39: 1065-1070.
42. Garcia EJ, Wardle BL, Hart AJ, Yamamoto N. Fabrication and multifunctional properties of a hybrid laminate with aligned carbon nanotubes grown In Situ. *Compos Sci Technol* 2008; 68: 2034-2041.
43. Blanco J, Garcia EJ, Guzman de Villoria R, Wardle BL. Limitations of Mode I interlaminar toughening of composites reinforced with aligned carbon nanotubes. *J Compos Mater* 2009; 43: 825-841.
44. Wicks S, Guzman de Villoria R, Wardle BL. Interlaminar and intralaminar reinforcement of composite laminates with aligned carbon nanotubes. *Compos Sci Technol* 2010; 70: 20-28.
45. Gibson T, Putthanarat S, Fielding JC, Drain A, Will K, Stoffel M. Conductive nanocomposites: focus on lightning strike protection. *Proc. Intl SAMPE Tech Conf and Exhibition – From Art to Science: Advancing Mater and Proc Engr* 2007 (on CD).
46. Allaoui A, Bai S, Cheng HM, Bai JB. Mechanical and electrical properties of a MWNT/epoxy composite. *Compos Sci Technol* 2002; 62: 1993-1998.
47. Qiu J, Zhang C, Wang B, Liang R. Carbon nanotube integrated multifunctional composites. *Nanotech* 2007; 18: 275708.
48. Kalaitzidou K, Fukushima H, Drzal LT. Multifunctional polypropylene composites produced by incorporation of exfoliated graphite nanoplatelets. *Carbon* 2007; 45: 1446-1452.
49. Cebeci H, Guzman de Villoria R, Hart AJ, Wardle BL. Multifunctional properties of high volume fraction aligned carbon nanotube polymer composites with controlled morphology. *Compos Sci Technol* 2009; 69: 2649-2656.
50. Sandler JKW, Kirk JE, Kinloch IA, Shaffer MSP, Windle AH. Ultra-low electrical percolation threshold in carbon-nanotube-epoxy composites. *Polymer* 2003; 44: 5893-5899.
51. Li J, Ma PC, Chow WS, To CK, Tang BZ, Kim J-K. Correlations between percolation threshold, dispersion state, and aspect ratio of carbon nanotubes. *Adv Funct Mater* 2007; 17: 3207-3215.
52. Thostenson ET, Ziaee S, Chou T-W. Processing and electrical properties of carbon nanotube/vinyl ester nanocomposites. *Compos Sci Technol* 2009; 69: 801-804.
53. Li C, Thostenson ET, Chou T-W. Effect of nanotube waviness on the electrical conductivity of carbon nanotube-based composites. *Compos Sci Technol* 2008; 68: 1445-1452.
54. Shenogina N, Shenogin S, Xue L, Keblinski P. On the lack of thermal percolation in carbon nanotube composites. *Appl Phys Lett* 2005; 87: 133106.
55. Biercuk MJ, Llaguno MC, Radosavljevic M, Hyun JK, Johnson AT. Carbon nanotube composites for thermal management. *Appl Phys Lett* 2002; 80(15): 2767-2769.
56. Bonnet P, Sireude D, garnier B, Chauvet O. Thermal properties and percolation in carbon nanotube-polymer composites. *Appl Phys Lett* 2007; 91: 201910.
57. Kim YA, Kamio S, Tajiri T, Hayashi T, Song SM, Endo M, Terrones M, Dresselhaus MS. Enhanced thermal conductivity of carbon fiber/phenolic resin composites by the introduction of carbon nanotubes. *Appl Phys Lett* 2007; 90: 093125.
58. Ganguli S, Roy AK, Anderson DP. Improved thermal conductivity for chemically functionalized exfoliated graphite/epoxy composites. *Carbon* 2008; 46(5): 806-817.
59. Sih S, Ganguli S, Roy AK, Qu L, Dai L. Enhancement of through-thickness thermal conductivity in adhesively bonded joints through using aligned carbon nanotubes. *Compos Sci Technol* 2008; 68: 658-665.

60. Lesieutre GA, Davis CL. Can a coupling coefficient of a piezoelectric device be higher than those of its active material? *J Intel Mater Syst Struct* 1997; 8(10): 859-867.
61. Giurgiutiu V, Zagari AN. Characterization of piezoelectric wafer active sensors. *J Intel Mater Syst Struct* 2001; 11(12): 959-976.
62. Muralt P, Polcawich RG, Troiler-McKinstry S. Piezoelectric thin films for sensors, actuators and energy harvesting. *MRS Bulletin* 2009; 34(9): 658-664.
63. Tadigadapa S, Mateti K. Piezoelectric MEMS sensors: state-of-the-art and perspectives. *Meas Sci Technol* 2009; 20: 092001.
64. Hagood NW, Bent AA. Development of piezoelectric fiber composites for structural actuation. *Proc 34th AIAA Structures, Structural Dynamics and Mater Conf* 1993; AIAA Paper No. 93-1717: La Jolla, CA.
65. Bent AA, Hagood NW, Rogers JP. Anisotropic actuation with piezoelectric fiber composites. *J Intel Mater Syst Struct* 1995; 6: 338-349.
66. Fernandez JF, Dogan A, Zhang QM, Tressler JF, Newnham RE. Hollow piezoelectric composites. *Sensors and Actuators A* 1996; 51: 183-192.
67. Brei D, Cannon BJ. Piezoceramic hollow fiber active composites. *Compos Sci Technol* 2004; 64: 245-261.
68. Lin Y, Sodano HA. Concept and model of a piezoelectric structural fiber for multifunctional composites. *Compos Sci Technol* 2008; 68: 1911-1918.
69. Lin Y, Sodano HA. Fabrication and electromechanical characterization of a piezoelectric structural fiber for multifunctional composites. *Adv Funct Mater* 2009; 19: 592-598.
70. Fuchs A, Shang Q, Elkins J, Gordaninejad F, Evrensel C. Development and characterization of magnetorheological elastomers. *J Appl Polym Sci* 2007; 105: 2497-2508.
71. Lin M, Chang F-K. The manufacture of composite structures with a built-in network of piezoceramics. *Compos Sci Technol* 2002; 62: 919-939.
72. Qing XP, Beard S, Kumar A, Ooi TK, Chang F-K. Built-in sensor network for structural health monitoring of composite structure. *J Intel Mater Syst Struct* 2007; 18(1): 39-49.
73. Wu Z, Qing XP, Chang F-K. Damage detection for composite laminate plates with a distributed hybrid PZT/FBG sensor network. *J Intel Mater Syst Struct* 2009; 20: 1069-1077.
74. Su Z, Wang X, Chen Z, Ye L, Wang D. A built-in active sensor network for health monitoring of composite structures. *Smart Mater Struct* 2006; 15: 1939-1949.
75. Su Z, Wang X, Chen Z, Ye L. Damage assessment of multi-layered composite structure using an embedded active sensor network. *Key Engr Mater* 2007; 334-335: 461-464.
76. Watkins SE, Akhavan F, Dua R, Chandrashekhara K, Wunsch DC. Impact-induced damage characterization of composite plates using neural networks. *Smart Mater Struct* 2007; 16: 515-524.
77. Haywood J, Coverley PT, Staszewski WJ, Worden K. An automated impact monitor for a composite panel employing smart sensor technology. *Smart Mater Struct* 2005; 14: 265-271.
78. Yu L, Cheng L, Yam LH, Yan YJ, Jiang JS. Online damage detection for laminated composite shells partially filled with fluid. *Compos Struct* 2007; 80: 334-342.
79. Srivastava A, Agarwal A, Chakraborty D, Dutta A. Control of smart laminated FRP structures using artificial neural networks. *J Reinf Plast Compos* 2005; 24(13): 1353-1364.
80. Loh KJ, Kim J, Lynch JP, Kam NWS, Kotov N. Multifunctional layer-by-layer carbon nanotube-polyelectrolyte thin films for strain and corrosion sensing. *Smart Mater Struct* 2007; 16: 429-438.
81. Loh KJ, Lynch JP, Kotov N. Passive wireless sensing using SWMT-based multifunctional thin film patches. *Intl J Appl Electromag Mech* 2008; 28: 887-94.
82. Olek M, Ostrander J, Jurga S, Mohwald H, Kotov N, Kempa K, Giersig M. Layer-by-layer assembled composites from multiwall carbon nanotubes with different morphologies. *Nano Lett* 2004; 4(10): 1889-1895.
83. Shim BS, Starkovich J, Kotov N. Multilayer composites from vapor-grown carbon nano-fibers. *Compos Sci Technol* 2006; 66: 1174-1181.
84. Sodano HA, Inman DJ, Park G. Generation and storage of electricity from power harvesting devices. *J Intel Mater Syst Struct* 2005; 16(1): 67-75.
85. Pereira T, Guo Z, Nieh S, Arias J, Hahn HT. Embedding thin-film lithium energy cells in structural composites. *Compos Sci Technol* 2008; 68: 1935-1941.

86. Pereira T, Guo Z, Nieh S, Arias J, Hahn HT. Energy storage structural composites: a review. *J Compos Mater* 2009; 43(5): 549-560.
87. Kim HS, Kang JS, Park JS, Hahn HT, Jung HC, Joung JW. Inkjet printed electronics for multifunctional composite structure. *Compos Sci Technol* 2009; 69(7-8): 1256-1264.
88. Liu P, Sherman E, Jacobsen A. Design and fabrication of multifunctional structural batteries. *J Power Sources* 2009; 189(1): 646-650.
89. Snyder JF, Carter RH, Wetzel ED. Electrochemical and mechanical behavior in mechanically robust solid polymer electrolytes for use in multifunctional structural batteries. *Chem Mater* 2007; 19(15): 3793-3801.
90. Snyder JF, Wong EL, Hubbard CW. Evaluation of commercially available carbon fibers, fabrics and papers for potential use in multifunctional energy storage applications. *J Electrochem Soc* 2009; 156(3): A215-A224.
91. O'Brien DJ, Baechle DM, Wetzel ED. Multifunctional structural composite capacitors for U. S. Army applications. *Proc Intl SAMPE Tech Conf 2006, 38th Fall Tech Conf: Global Adv Mater Proc Engr.*
92. Baechle DM, O'Brien DJ, Wetzel ED. Design and processing of structural composite capacitors. *Proc Intl SAMPE Symposium and Exhibition 2007, M and P – From Coast to Coast and Around the World.*
93. Luo X, Chung DDL. Carbon fiber /polymer matrix composites as capacitors. *Compos Sci Technol* 2001; 61(6): 885-888.
94. Lin Y, Sodano HA. Characterization of multifunctional structural capacitors for embedded energy storage. *J Appl Phys* 2009; 106: 114108.
95. White SR, Sottos NR, Geubelle PH, Moore JS, Kessler MR, Sriram SR, Brown EN, Viswanathan S. Autonomic healing of polymer composites. *Nature* 2001; 409: 794-797.
96. Brown EN, Sottos NR, White SR. Fracture testing of a self-healing polymer composite. *Experimental Mechanics* 2002; 42: 372-379.
97. Caruso MM, Blaiszik BJ, White SR, Sottos NR, Moore JS. Full recovery of fracture toughness using a nontoxic solvent-based self-healing system. *Adv Funct Mater* 2008; 18(13): 1898-1904.
98. Brown EN, White SR, Sottos NR. Retardation and repair of fatigue cracks in a microcapsule toughened epoxy composite – Part I: Manual infiltration. *Compos Sci Technol* 2005; 65: 2466-2473.
99. Brown EN, White SR, Sottos NR. Retardation and repair of fatigue cracks in a microcapsule toughened epoxy composite – Part II: In situ self-healing. *Compos Sci Technol* 2005; 65: 2474-2480.
100. Brown EN, White SR, Sottos NR. Fatigue crack propagation in microcapsule toughened epoxy. *J Mater Sci*; 41(19): 6266-6273.
101. Patel AJ, Sottos NR, Wetzel ED, White SR. Autonomic healing of low-velocity impact damage in fiber-reinforced composites. *Compos Part A: Appl Sci Manuf* 2010; 41(3): 360-368.
102. Cho SH, White SR, Braun PV. Self-healing polymer coatings. *Adv Mater* 2009; 21(6) 645-649.
103. Toohey KS, Sottos NR, Lewis JA, Moore JS, White SR. Self-healing materials with microvascular networks. *Nature Mater* 2007; 6: 581-585.
104. Kirk JG, Naik S, Moosbrugger JC, Morrison DJ, Volkov D, Sokolov I. Self-healing epoxy composites based on the use of nanoporous silica capsules. *Int J Fract* 2009; 159(1): 101-102.
105. Privman V, Dementsov A, Sokolov I. Modeling of self-healing polymer composites reinforced with nanoporous glass fibers. *J Comput Theor Nanosci* 2007; 4(1): 190-193.
106. Williams G, Trask R, Bond I. A self-healing carbon fibre reinforced polymer for aerospace applications. *Compos Part A: Appl Sci Manuf* 2007; 38(6): 1525-152.
107. Yin T, Rong MZ, Zhang MQ, Zhao JQ. Durability of self-healing woven glass fabric/epoxy composites. *Smart Mater Struct* 2009; 18(7): 074001.
108. Balazs AC. Modeling self-healing materials. *Mater Today* 2007; 10(9): 18-23.
109. Barbero EJ, Breco F, Lonetti P. Continuum damage-healing mechanics with application to self-healing. *Int J Damage Mech* 2005; 14(1): 51-81.
110. Maiti S, Shankar C, Geubelle PH, Kieffer J. Continuum and molecular level modeling of fatigue crack retardation in self-healing polymers. *J Engr Mater Technol* 2006; 128(4): 595-602.
111. Geubelle PH, Maiti S. Cohesive modeling of fatigue crack retardation in polymers: Crack closure effect. *Engr Fract Mech* 2006; 73(1): 22-41.
112. Park JS, Kim HS, Hahn HT. Healing behavior of a matrix crack on a carbon fiber/mendomer composite. *Compos Sci Technol* 2009; 69(7-8): 1082-1087.

113. Chung DDL. Materials for electromagnetic interference shielding. *J Mater Perform* 2000; 9(3): 350-354.
114. Geetha S, Kumar KKS, Rao CRK, Vijayan M, Trivedi DC. EMI shielding: Methods and materials: A review. *J Appl Polym Sci* 2009; 112(4), 2073-2086.
115. Wang Y, Jing X. Intrinsically conducting polymers for electromagnetic interference shielding. *Polym Adv Technol* 2005; 16(4): 344-351.
116. Jia QM, Li JB, Wang LF, Zhu JW, Zheng M. Electrically conductive epoxy resin composites containing polyaniline with different morphologies. *Mater Sci Engr A* 2007; 448: 356-360.
117. Huang Y, Li N, Ma Y, Du F, Li F, He X, Lin X, Gao H, Chen Y. The influence of single-walled carbon nanotube structure on the electromagnetic interference shielding efficiency of its epoxy composites. *Carbon* 2007; 45: 1614-1621.
118. Al-Saleh MH, Sundararaj U. Electromagnetic interference shielding mechanisms of CNT/polymer composites. *Carbon* 2009; 47: 1738-1746.
119. Yang Y, Gupta MC, Dudley KL, Lawrence RW. Electromagnetic interference shielding characteristics of carbon nanofiber-polymer composites. *J Nanosci Nanotech* 2007; 7(2) 549-554.
120. Al-Saleh MH, Sundararaj U. A review of vapor grown carbon nanofiber/polymer conductive composites. *Carbon* 2009; 47(1): 2-22.
121. Thill C, Etches J, Bond I, Potter K, Weaver P. Morphing skins. *Aeronautical J* 2008; 112(1129): 117-139.
122. Wildschek A, Havar T, Plotner K. An all-composite, all-electric, morphing trailing edge for flight control of a blended wing body airliner. *Proc Inst Mech Engrs, Part G: J Aerosp Engr* 2010; 224(1): 1-9.
123. Hartl DJ, Lagoudas DC, Calkins FT, Mabe JH. Use of a Ni60Ti shape memory alloy for active jet engine chevron application: I. thermomechanical characterization. *Smart Mater Struct* 2010; 19(1): 015020.
124. Hartl DJ, Mooney JT, Lagoudas DC, Calkins FT, Mabe JH. Use of a Ni60Ti shape memory alloy for active jet engine chevron application: II. Experimentally validated numerical analysis. *Smart Mater Struct* 2010 19(1): 015021.
125. Mudupu V, Trabia MB, Yim W, Weinacht P. Design and validation of a fuzzy logic controller for a smart projectile fin with a piezoelectric macro-fiber composite bimorph actuator. *Smart Mater Struct* 2008; 17(3):
126. Thomas JP, Qidwai MA. Mechanical design and performance of composite multifunctional materials. *Acta Mater* 2004; 52: 2155-2164.
127. Thomas JP, Qidwai MA. The design and application of multifunctional structure-battery material systems. *JOM* 2005; 57(3): 18-24.
128. Tuss J, Lockyer A, Alt K, Uldrich F, Kinslow R, Kudva J, Goetz A. Conformal load bearing antenna structure. *Proc AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dyn Mater Conf* 1996; 2: 836-843.
129. Lockyer AJ, Alt K, Kinslow RW, Kan H-P, Kudva JN, Tuss J, Goetz A. Development of a structurally integrated conformal load-bearing multifunction antenna: Overview of the Air Force Smart Skin Structures Technology Demonstration Program. *Proc. SPIE Smart Struct Mater Conf* 1996; 2722: 55-64.
130. Berden MJ, McCarville DA. Structurally integrated X-band antenna large scale component wing test. *Proc Int SAMPE Symp Exhib: M and P- From Coast to Coast and Around the World* 2007; 52.
131. Lockyer AJ, Alt KH, Kudva JN, Tuss J. Air vehicle integration issues and considerations for CLAS successful implementation. *Proc SPIE Smart Struct Mater Conf* 2001; 4332: 48-59.
132. Yao L, Qiu Y. Design and fabrication of microstrip antennas integrated in three dimensional orthogonal woven composites. *Compos Sci Technol* 2009; 69: 1004-1008.
133. Yao L, Wang X, Xu F, Zhao D, Jiang M, Qiu Y. Fabrication and impact performance of three dimensionally integrated microstrip antennas with microstrip and coaxial feeding. *Smart Mater Struct* 2009; 18: 095034.
134. Matsuzaki R, Melnykowycz M, Todoroki A. Antenna/sensor multifunctional composites for the wireless detection of damage. *Compos Sci Technol* 2009; 69: 2507-2513.
135. Wirtz R, Zhao T, Jiang Y. Thermal and mechanical characterization of a multifunctional thermal energy storage structure. *IEEE Trans Component Packaging Technol* 2009; 32(1): 53-62.
136. Queheillalt DT, Carbajal G, Peterson GP, Wadley HNG. A multifunctional heat pipe sandwich panel structure. *Int J Heat Mass Transf* 2008; 51(1-2): 312-326.
137. Ozaki T, Takeya H, Kume M, Sekine K. Multifunctional composite structures for space satellites. *SAMPE J* 2008; 44(2): 6-11.

138. Silverman E. Multifunctional carbon foam development for spacecraft applications. *SAMPE J* 2005; 41(3): 19-27.
139. Cameron CJ, Wennhage P, Goransson P, Rahmqvist S. Structural-acoustic design of a multifunctional sandwich panel in an automotive context. *J Sand Struct Mater* 2010; published Online First January 28, 2010.
140. Vaidya AS, Vaidya UK, Uddin N. Impact response of three-dimensional multifunctional sandwich composite. *Mater Sci Engr* 2008; 472(1-2): 52-58.
141. Lee JL, Zeng C, Cao X, Han X, Shen J, Xu G. Polymer nanocomposite foams. *Compos Sci Technol* 2005; 65(15-16): 2344-2363.
142. Suh WH, Suh Y-H, Stucky GD. Multifunctional nanosystems at the interface of physical and life sciences. *Nano Today* 2009; 4(1): 27-36.
143. Haglund E, Seale-Goldsmith MM, Leary JF. Design of multifunctional nanomedical devices. *Annals Biomed Engr* 2009; 37(10): 2048-2063.
144. Park K, Lee S, Kang E, Kim K, Choi K, Kwon IC. New generation of multifunctional nanoparticles for cancer imaging and therapy. *Adv Funct Mater* 2009; 19(10): 1553-1566.
145. Corr SA, Rakovich YP, Gun'ko YK. Multifunctional magnetic-fluorescent nanocomposites for biomedical applications. *Nanoscale Res Lett* 2008; 3(3): 87-104.
146. Lou XW, Archer LA, Yang Z. Hollow micro/nanostructures: synthesis and applications. *Adv Mater* 2008; 20: 3987-4019.
147. An K, Hyeon T. Synthesis and biomedical applications of hollow nanostructures. *Nano Today* 2009; 4(4): 359-373.
148. Shahinpoor M, Kim K. Ionic polymer-metal composites: I. Fundamentals. *Smart Mater Struct* 2001; 10: 1-15.
149. Kim K, Shahinpoor M. Ionic polymer-metal composites: II. Manufacturing techniques. *Smart Mater Struct* 2003; 12: 65-67.
150. Shahinpoor M, Kim K. Ionic polymer-metal composites: III. Modeling and simulation as biomimetic sensors, actuators, transducers and artificial muscles. *Smart Mater Struct* 2004; 13: 1362-1388.
151. Shahinpoor M, Kim K. Ionic polymer-metal composites: IV. Industrial and medical applications. *Smart Mater Struct* 2005; 14: 197-214.
152. Bar-Cohen Y. Electroactive polymers as artificial muscles: a review. *J Spacecraft Rockets* 2002; 39: 822-827.
153. Qi Y, Jafferis NT, Lyons Jr K, Lee CM, Ahmad H, McAlpine MC. Piezoelectric ribbons printed onto rubber for flexible energy conversion. *Nano Letters* 2010; 10: 524-528.
154. Shim BS, Chen W, Doty C, Xu C, Kotov NA. Smart electronic yarns and wearable fabrics for human biomonitors made by carbon nanotube coating with polyelectrolytes. *Nano Letters* 2008; 8(12): 4151-4157.
155. Granstrom J, Feenstra J, Sodano HA, Farinholt K. Energy harvesting from a backpack instrumented with piezoelectric shoulder straps. *Smart Mater Struct* 2007; 16(5): 1810-1820.
156. Rai KN, Singh D. Impact resistance behavior of polymer nanocomposite transparent panels. *J Compos Mater* 2009; 43(2): 139-151.
157. Liu Y, Hedin NE, Fong H. Polycarbonate/poly(methyl methacrylate) nanofiber composites with improved impact strength. *J Appl Mater* 2008; 40(3): 33-42.
158. Rojanapitayakorn P, Mather PT, Goldberg AJ, Weiss RA. Optically transparent self-reinforced poly(ethylene terephthalate) composites: molecular orientation and mechanical properties. *Polymer* 2005; 46(3): 761-773.
159. Song J-Y, Kim J-W, Suh K-D. Poly(methyl methacrylate) toughening with refractive index-controlled core-shell composite particles. *J Appl Polymer Sci* 1999; 71(10): 1607-1614.
160. Huang J, Yang B, Huang D, Shen J. Core-shell nanoparticles reinforced polystyrene with no effect on its transparency. *Int J Poly Mater* 1997; 35(1-4): 13-19.