

UNCLASSIFIED



AD NUMBER

AD-A950 590

CLASSIFICATION CHANGES

TO **UNCLASSIFIED**

FROM **CONFIDENTIAL**

AUTHORITY

OCA; Dec 31, 1986

THIS PAGE IS UNCLASSIFIED

UNCLASSIFIED



AD NUMBER

AD-A950 590

NEW LIMITATION CHANGE

TO

DISTRIBUTION STATEMENT: A

Approved for public release; Distribution is unlimited.

LIMITATION CODE: 1

FROM

No DoD Distr Scty Cntrl St'mt Provided

AUTHORITY

Cmdr, Watertown Arsenal Labs; Oct 31, 1987

THIS PAGE IS UNCLASSIFIED

AD A950590

AD

JUN 23 1961



UNCLASSIFIED

AD 321442

WAL TR 161.3/1 (C) ✓

WATERTOWN ARSENAL LABORATORIES

BALLISTIC EVALUATION OF ROLLED HOMOGENEOUS STEEL ARMOR
WITH TUNGSTEN CARBIDE AND TITANIUM CARBIDE FACING (U)

TECHNICAL REPORT NO. WAL TR 161.3/1 (C)

BY

DONINIC A. PICCIGNE

DECEMBER 1960

DTIC
ELECTE
JUN 18 1981

19990430228

FILE COPY

DD FORM 1010-11-000001 - MATERIALS FOR ARMOR AND
PROTECTION AGAINST OTHER HAZARDS

79-61-C
241

68-61-C

OFFICIAL FILE COPY

WATERTOWN ARSENAL
WATERTOWN

UNCLASSIFIED

81 6 15 212

[REDACTED]

ASTIA AVAILABILITY NOTICE

U. S. Military agencies may obtain copies of this report directly from Armed Service Technical Information Agency, Arlington Hall Station, Arlington 12, Virginia. Other qualified ASTIA users should request through Commanding Officer, Watertown Arsenal, Watertown 72, Massachusetts, ATTENTION: Chief, Technical Information Section.

DISPOSITION INSTRUCTIONS

Department of Defense addressees

This classified report will be destroyed in accordance with AR 380-3 when no longer required.

All other addressees

This report contains information affecting the national defense of the United States within the meaning of the Espionage Laws, Title 18, U.S.C., Sections 793 and 794, the transmission or revelation of which in any manner to an unauthorized person is prohibited by law. When no longer required, this document must be returned either to Watertown Arsenal or to the contracting officer.

[REDACTED]

[REDACTED]
[REDACTED]
UNCLASSIFIED

Terminal ballistics,
testing

Ballistic limits -
protection

⑥ BALLISTIC EVALUATION OF ROLLED HOMOGENEOUS STEEL ARMOR
WITH TUNGSTEN CARBIDE AND TITANIUM CARBIDE FACING (H)

⑨ Technical Report No. WAL-TR-161.3/1(C) ⑭

By

⑩ Dominic A. Piccione

⑫ 38

⑪ Dec 1960

ONS CODE 5010.11.8090051 - Materials for Armor and
Protection against other Hazards

WATERTOWN ARSENAL
[REDACTED]
[REDACTED]

UNCLASSIFIED xlv
370150

UNCLASSIFIED

TITLE

BALLISTIC EVALUATION OF ROLLED HOMOGENEOUS STEEL ARMOR
WITH TUNGSTEN CARBIDE AND TITANIUM CARBIDE FACING (U)

ABSTRACT (U)

(C) Ballistic testing was conducted to determine the comparative performance of tungsten carbide steel and titanium carbide steel composite armor when attacked by cal. .40 H19B WC cores, cal. .50 AP M2 projectiles, 20MM fragment simulating projectiles, and cal. .40 AP T33 scale model projectiles, at various obliquities. On an areal density basis the TiC composite armor was approximately equivalent to steel, while the WC composite armor was inferior to steel. The results obtained do not justify consideration of these armor configurations for Ordnance applications.

Dominic A. Piccione
DOMINIC A. PICCIONE
Mechanical Engineer

APPROVED:

J. F. Sullivan
J. F. SULLIVAN
Director
Watertown Arsenal Laboratories

Accession For	
NTIS GRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
Distribution/	
Availability Codes	
Dist	Avail. and/or
	Spec. Del.

REPORT APPROVED
Date- 23 Jan 61
WAL Board of Review
Chairman- *W80*

UNANNOUNCED

UNCLASSIFIED

INTRODUCTION (U)

(C) Kennametal Corporation, under Contract DA-19-066-ORD-2641, conducted preliminary tests to determine the effectiveness of tungsten carbide (WC) and titanium carbide (TiC) facing on steel armor for the defeat of steel and tungsten carbide projectiles. Cal. .40 steel and WC projectiles were fired at 1-3/4-inch-thick steel armor, placed at 30° obliquity, without facing and with 1/4-inch-thick WC and TiC facings. The results obtained indicated that the use of a hard facing material might improve the ballistic performance of steel armor. It must be pointed out, however, that for these tests the difference in areal density between the uncoated and coated plates was not taken into account. No direct comparison could be made between the composite armor and solid steel of the same areal density since the ballistic limits were above the muzzle velocity of the available guns.

(U) In order to evaluate fully the effect of such facing materials, Watertown Arsenal Laboratories has conducted a series of ballistic tests to determine the comparative ballistic performance of WC and TiC facings placed on rolled homogeneous steel armor.

MATERIALS (U)

(U) Tungsten carbide facings of 1/16" and 1/8" thicknesses and titanium carbide facings of 1/16", 1/8" and 1/4" thicknesses were employed in the form of hexagonally shaped platelets (Figure 1) measuring 0.425" across the flats. The tungsten carbide consisted of 85% WC + 15% Co nominal composition cold pressed and sintered to a hardness of 88 Rockwell A, while the titanium carbide consisted of 70% TiC + 30% Ni which was cold pressed and sintered to a hardness of approximately 87 Rockwell A.

(U) Rolled homogeneous steel armor of various thicknesses was cut to 12" x 12" sizes. Each plate was Blanchard ground to a thickness such that a predetermined areal density would be obtained. All steel armor employed had previously been quenched to martensite and tempered to a hardness of 300 Bhn subsequent to meeting the requirements of Specification MIL-A-12560. Chemical composition of the steel armor is contained in Table I.

(U) Both types of facing materials and the steel armor were sand-blasted to obtain the clean surfaces necessary for satisfactory bonding. Neither facing nor steel was handled with bare hands subsequent to sand-blasting since oils and moisture transferred to the materials in handling would prevent adequate bonding during brazing. A 1"-wide steel frame was placed along the perimeter of the plate to prevent the facing material from "floating" off during the brazing operation. Two 6" x 12" strips of 0.005"-thick silver solder, having the composition shown in Table I, were placed on each plate and flux applied. The platelets were positioned, each plate requiring the placing of approximately 700 individual pieces.

[REDACTED]

The entire assembly was then placed for two hours in a furnace which had been preheated to 1375°F. The plates were air cooled from the furnace with no evidence of excessive warping even though the rate of expansion of steel is about twice that of the facing materials used. Photographs of two plates taken prior to ballistic testing are shown in Figures 2 and 3.

(U) As a result of the brazing operation, the steel plate was softened to an average Brinell hardness of 211. Metallographic examination of the steel revealed that it still consisted of a tempered martensitic structure which indicates that the original structure was not destroyed by the high brazing temperature since the austenitizing temperature was not exceeded. Photomicrographs representing three steel plates are presented in Figure 4.

(U) Ballistic data were obtained using 20MM fragment simulating projectiles, caliber .40 H&B WC cores, caliber .50 AP M2 projectiles, and caliber .40 AP T33 scale model projectiles, at various obliquities. The WC cores were cold pressed and sintered from 87% WC + 13% Co to a hardness of 89 Rockwell A. The scale model projectiles were machined from FXS-318 steel, water quenched and stress relieved to a hardness of 63 Rockwell C, followed by base tempering to develop a hardness gradient to 45 Rockwell C at the base. The caliber .50 AP M2 projectiles were standard rounds. Drawings of all projectiles are presented in Figure 5.

BALLISTIC TEST PROCEDURE (U)

(U) The detailed outline of the ballistic test conditions is presented in Table II.

(U) Ballistic testing was conducted to determine protection-ballistic limits* consisting of the two highest partial penetrations and the two lowest complete penetrations within a velocity spread of 125 fps. When the velocity spread was greater than 125 fps or when insufficient rounds had been fired, a two-round ballistic limit was computed. Care was exercised after each round fired to insure that the next round would impact a plate area where the platelets had not been removed by a previous impact. A 0.100"-thick sheet of Hadfield-Manganese steel, having a hardness of 40 Rockwell C, was placed in front of the facing to confine the facing during impact.

*Complete penetration occurs when plate and/or projectile fragments penetrate a 0.020"-thick sheet of Duralumin placed 6" behind the armor.

~~CONFIDENTIAL~~

UNCLASSIFIED

RESULTS AND DISCUSSION (U)

(U) The ballistic data obtained both by Watertown Arsenal Laboratories and Kennametal Corporation are presented in Table III. Round by round results are presented in Appendix A.

Ballistic Performance of WC-Steel Armor (U)

(C) Ballistic data obtained with caliber .40 AP T33 scale model projectiles are plotted as a function of areal density in Figure 6. On the average, the hard-faced armor was approximately 6% inferior to steel targets of equal areal densities. Hadfield-Manganese sheet had been used for the 45 degree test condition while none had been used for the 30 and 60 degree test conditions. The curves clearly show that the hard-faced armor was nearly equivalent to the steel except for one 30 degree and three 45 degree obliquity conditions. These data did not fit the curve, falling far below the data obtained. As this anomaly was noted elsewhere a discussion will be presented in a following section. It suffices to say that the limited data obtained does not indicate that the hard-faced armor will offer any significant increase in protection.

(C) A graphical presentation of the limited ballistic data obtained with caliber .50 AP M2 projectiles is presented in Figure 7. This curve clearly shows the inferiority of the composite armor. At 30 degrees obliquity there is a difference of 1372 fps in the ballistic limit, which represents a 48% difference in performance between the hard-faced armor and equivalent steel targets. On an areal density basis the composite armor averaged approximately 43% inferior to solid steel armor.

(C) Ballistic data obtained with caliber .40 H19B WC cores is plotted versus obliquity in Figure 8. From this graph it is obvious that the difference in performance is slight. The ballistic limits ranged from 12 - 660 fps less than those of equivalent steel targets. This represents an average difference in performance of approximately 8%.

Ballistic Performance of TiC-Steel Armor (U)

(C) Ballistic data obtained with caliber .40 AP T33 scale model projectiles is plotted as a function of areal density in Figure 9. On the average, the hard-faced armor was approximately 2% superior to steel targets having the same areal density. Inspection of the data reveals that at an equivalent thickness of 0.700" the 30 and 45 degree ballistic limits were less than those at 0.600" equivalent thickness. If these anomalous data points are ignored, the composite armor would still be only 3% superior to equivalent steel targets, representing at best a marginal improvement.

(C) Ballistic data obtained with 20MM fragment simulating projectiles is plotted versus areal density in Figure 10. The limited data obtained indicates that the hard-faced armor is approximately 14% inferior to steel

~~CONFIDENTIAL~~

UNCLASSIFIED

~~CONFIDENTIAL~~

targets of the same areal density. Inspection of the curves reveals that the ballistic limits for the hard-faced armor ranged 300 - 862 fps less than those of equivalent steel targets. At only one condition, where no ballistic limit was obtained for the hard-faced armor, did it show any indication of being superior to solid steel targets. Even at this point it is estimated that the hard-faced armor would have been less than 10% superior to a steel target of equal density. This statement is based on the fact that a complete penetration was almost obtained, indicative that the ballistic limit was nearly reached. From the data obtained a two-round Army ballistic limit* of approximately 4180 fps can be estimated.

Effect of Brazing (U)

(C) Photographs of five plates, two with WC facing and three with TiC facing, are shown in Figures 11 through 15. Figures 11 and 12 are examples of poor brazing since 85% of the platelets were removed as a result of only three impacts. Examples of good brazing can be seen in Figures 13 through 15. One plate withstood the impact of twelve rounds while another withstood six rounds, each round causing the removal of only small localized areas of platelets. The third plate represents an extreme condition of attack, 20mm fragment simulating projectiles at 60 degrees obliquity. Even under this severe test condition the facing withstood six impacts.

(C) Photomicrographs of three randomly selected brazed joints are shown in Figure 16. These photomicrographs show the presence of many large voids and evidence of flux entrapment. This would indicate that in order to obtain a uniform bond, free of these defects, the brazing should be done in an inert atmosphere or a vacuum. It is felt, however, that the bond obtained was adequate to permit reliable ballistic testing since all but 7 plates withstood the impact of 5 or more rounds.

GENERAL CONSIDERATIONS (U)

(C) It was previously mentioned that at several test conditions the ballistic data indicated decreasing ballistic resistance with increasing thickness of the hard facing. Since the object of this study is to determine whether the use of hard facing will significantly improve the ballistic performance of armor, it is beyond the scope of this report to explain this anomalous behavior. However, a possible reason for the behavior follows.

*Complete penetration occurs when light or the projectile can be seen from the rear of the plate.

~~CONFIDENTIAL~~

~~CONFIDENTIAL~~

(C) It has been demonstrated by many investigators that projectile nose-shatter generally occurs at obliquities greater than about 25 - 30 degrees at velocities above a certain minimum for the projectile and plate thickness involved.^{1,2,3} The shatter tendency for a given projectile increases with increasing velocity, increasing plate hardness, or increasing plate thickness. When a projectile suffers nose-shatter, it achieves penetration by a shear or punching mechanism involving a minimum of plastic deformation. The energy required for this plugging or punching process is largely dependent on the armor plate thickness at a constant obliquity of attack. Furthermore, for a constant obliquity, the velocity at which shatter occurs is very sensitive to plate thickness. Hence, it is conceivable that the projectile nose fractured into a very few large fragments against the 0.600" equivalent steel thickness armor, and shattered into many small fragments against the 0.700" equivalent steel thickness armor. It follows, then, that the penetration energies could be nearly equal, with the penetration of the thicker target possibly requiring less energy. The greater deformation around the penetrations of the 0.600" targets lend credence to this possibility.

(C) Although the use of a hard facing does not appear worthwhile for improvement of the ballistic performance of armor, the possibility of employing a hard material with a high neutron capture cross-section (such as boron carbide) for radiological protection should be investigated.

CONCLUSIONS (U)

(U) On the basis of the results obtained, the hard-faced armor is inferior to equivalent steel targets.

RECOMMENDATIONS (U)

(U) 1. Further ballistic testing of tungsten carbide and titanium carbide platelets is not recommended.

(C) 2. The use of hard facing placed over armor of specification hardness might increase the ballistic performance, but since the increase is expected to be marginal, ballistic testing of such an arrangement is not recommended.

(C) 3. The possibility of employing a hard material with a high neutron capture cross-section (such as boron carbide) for radiological protection should be investigated.

¹SEYER, G., Mechanism of Armor Penetration, Third Partial Report, Watertown Arsenal Laboratory, WAL 710/452-1, 30 March 1944.

²ABBOTT, K. E., Principles of Projectile Design for Penetration - Compound Conical-Nosed Tungsten Carbide Cores, Eleventh Partial Report, Watertown Arsenal Laboratories, WAL 752/231-11 (C), 25 October 1953.

³MASCIARICA, P. S., and RIFFIN, P. V., Principles of Armor Protection, Fifth Partial Report, Watertown Arsenal Laboratories, WAL 710/607-4 (C), 31 May 1956.

~~CONFIDENTIAL~~

TABLE I (U)

**CHEMICAL ANALYSIS OF COMPOSITE ARMOR
(Weight %)**

<u>STEEL ARMOR</u>								
<u>Element</u>	<u>C</u>	<u>Mn</u>	<u>Si</u>	<u>S</u>	<u>P</u>	<u>Ni</u>	<u>Cr</u>	<u>Mo</u>
	0.27	1.70	0.18	0.017	0.018	Trace	0.02	0.485
<u>SILVER SOLDER*</u>								
<u>Element</u>	<u>Ag</u>	<u>Cu</u>	<u>Zn</u>	<u>Cd</u>	<u>Ni</u>			
	80.0	15.5	15.5	18.0	8.0			

*This is manufacturer's advertised composition.

TABLE II (U)

DETAILS OF BALLISTIC TESTS CONDUCTED WITH WC AND TiC
COMPOSITE ARMOR

TUNGSTEN CARBIDE							
Projectile	Thickness (inch)		Areal Density (PSF)		Total Areal Density (PSF)	Equivalent Steel Thickness (inch)	Obliquity (degrees)
	Platelets	Steel Armor	Platelets	Steel Armor			
Cal. .40 AP T33	1/16	0.284	4.80	11.52	16.32	0.400	30
"	1/16	0.382	4.80	15.00	20.40	0.600	30
"	1/8	0.364	9.60	14.88	24.48	0.600	30
"	1/8	0.465	9.60	18.96	28.56	0.700	30
"	1/16	0.284	4.80	11.52	20.40*	0.600	45
"	1/16	0.382	4.80	15.00	24.48*	0.600	45
"	1/8	0.364	9.60	14.88	28.56*	0.700	45
"	1/8	0.465	9.60	18.96	32.64*	0.800	45
"	1/16	0.384	4.80	11.52	16.32	0.400	60
"	1/16	0.382	4.80	15.00	20.40	0.600	60
"	1/8	0.364	9.60	14.88	24.48	0.600	60
Cal. .50 AP M2	1/16	0.382	4.80	15.00	24.48*	0.600	30
"	1/16	0.382	4.80	15.00	24.48*	0.600	45
Cal. .40 H198 WC Cores	1/8	0.765	9.60	31.20	44.88*	1.100	30
"	1/8	0.765	9.60	31.20	44.88*	1.100	45
"	1/8	0.765	9.60	31.20	44.88*	1.100	60
TITANIUM CARBIDE							
Cal. .40 AP T33	1/8	0.408	3.77	15.63	24.48*	0.600	0
"	1/8	0.508	3.77	20.71	28.56*	0.700	0
"	1/16	0.352	1.89	14.43	20.40*	0.500	30
"	1/8	0.408	3.77	15.63	24.48*	0.600	30
"	1/8	0.508	3.77	20.71	28.56*	0.700	30
"	1/4	0.520	7.54	21.02	32.64*	0.800	30
"	1/4	0.615	7.54	25.10	36.72*	0.900	30
"	1/8	0.408	3.77	15.63	24.48*	0.600	45
"	1/8	0.508	3.77	20.71	28.56*	0.700	45
"	1/16	0.352	1.89	14.43	20.40*	0.500	60
"	1/8	0.408	3.77	15.63	24.48*	0.600	60
"	1/8	0.508	3.77	20.71	28.56*	0.700	60
20MM FSP	1/16	0.154	1.89	6.27	12.24*	0.300	30
"	1/16	0.352	1.89	14.43	20.40*	0.500	30
"	1/16	0.154	1.89	6.27	12.24*	0.300	60
"	1/16	0.352	1.89	14.43	20.40*	0.500	60

*1 0.100"-thick Hadfield-Manganese sheet was used.

CONFIDENTIAL

TABLE III (C)

COMPARATIVE BALLISTIC DATA OF WC AND TIC COMPOSITE ARMOR
AND ROLLED HOMOGENEOUS STEEL ARMOR (U)


TUNGSTEN CARBIDE FACING							
Projectile	Thickness (inch)		Steel Armor	Obliquity (degrees)	Protection (V ₅₀) Ballistic Limit		Superiority of Composite Armor Over Steel
	Equivalent Steel	Facing			Equivalent Steel (FPS) (Ref. 3)	Composite (FPS)	
Cal. .40 AP	0.400	1/16	0.284	30	2390	2425**	4.4
T33	0.500	1/16	0.362	30	2935	3002**	2.3
"	0.600	1/8	0.364	30	3490	3320**	-0.8
"	0.700	1/8	0.435	30	4020	4060**	1.0
"	0.800	1/16	0.284	45	3350	3217	-4.0
"	0.800	1/16	0.362	45	4030	3299	-18.1
"	0.700	1/8	0.364	45	4640	3673	-20.8
"	0.800	1/8	0.435	45	5440	4215	-22.5
"	0.400	1/16	0.284	60	3490	3595**	3.0
"	0.500	1/16	0.362	60	4350	4005**	-7.6
"	0.600	1/8	0.364	60	5110	5004**	-2.1
"	0.750*	--	0.750	30	4800**	--	--
"	1.224*	1/4	0.750	30	--	4800 HP**	--
Cal. .50 AP	0.600	1/16	0.362	30	2860	1488	-48.0
M2	0.600	1/16	0.362	45	3400	2100 HP	>-38.4
Cal. .40	1.100	1/8	0.765	30	2840	2535	-12.8
H19E WC	1.100	1/8	0.765	45	3100	3148	-0.4
Cores	1.100	1/8	0.765	60	5115	4455 HP	>-12.8
TITANIUM CARBIDE FACING							
Cal. .40 AP	0.600	1/8	0.408	0	2400	2624	12.2
T33	0.700	1/8	0.508	0	2700	3576	32.4
"	0.800	1/16	0.352	30	2935	2669	-12.5
"	0.800	1/8	0.408	30	3490	3656	4.8
"	0.700	1/8	0.508	30	4020	3620	-9.9
"	0.800	1/4	0.520	30	4810	6008	4.1
"	0.900	1/4	0.615	30	5600	4780 LC	--
"	0.800	1/8	0.408	45	4030	4199	4.2
"	0.700	1/8	0.508	45	4640	4127	-11.2
"	0.800	1/16	0.352	60	4350	4028	-7.4
"	0.800	1/8	0.408	60	5110	5215	2.1
"	0.700	1/8	0.508	60	5770	5790 HP	>0.4
"	0.750*	--	0.750	30	4800	--	--
"	0.935*	1/4	0.750	30	--	4800 HP	--
20MM FFP	0.300	1/16	0.154	30	1940	1940	-15.6
"	0.500	1/16	0.352	30	2973	2568	-13.6
"	0.300	1/16	0.154	60	2840	1978	-30.4
"	0.500	1/16	0.352	60	4220	4410 HP	>4.6
Cal. .40 WC	1.000*	--	1.000	30	2600**	--	--
Cores	1.185*	1/4	1.000	30	--	>3850**	--

NOTE: HP - Highest partial penetration
LC - Lowest complete penetration


*Kammetal Corporation data.

**Jo Hadfield-Manganese sheet used.


CONFIDENTIAL

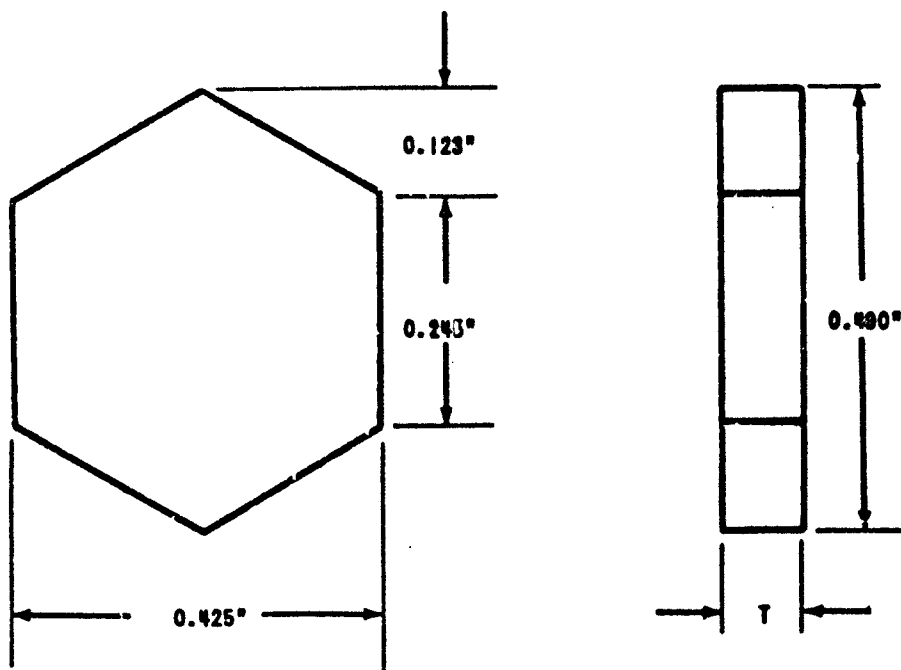


DIMENSION OF FACING USED FOR FABRICATION OF COMPOSITE ARMOR

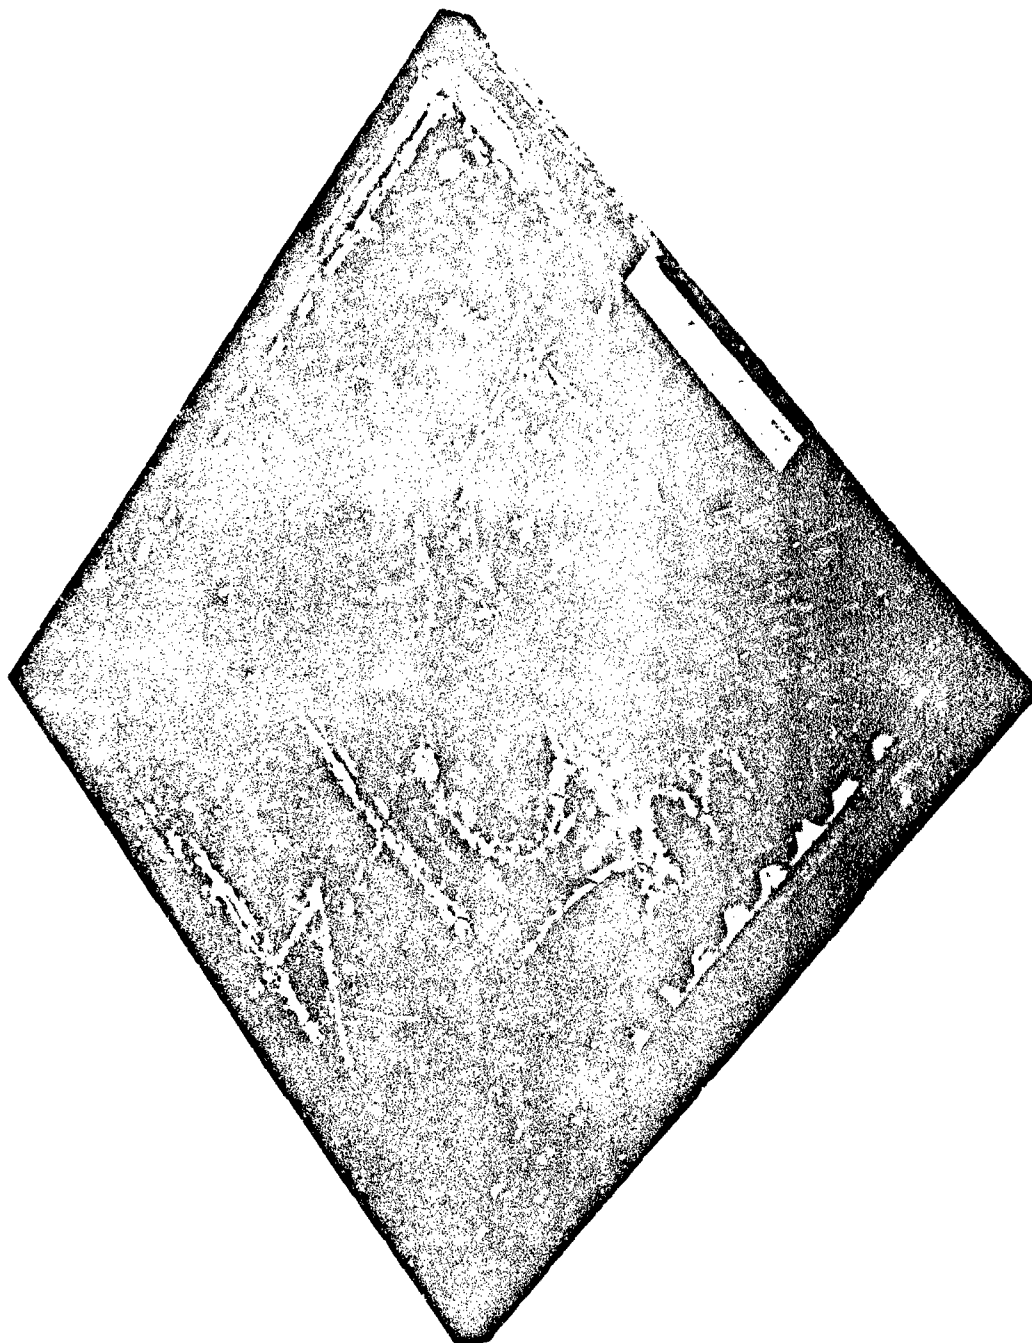


TUNGSTEN CARBIDE COMPOSITE ARMOR PLATE PRIOR TO BALLISTIC TESTING

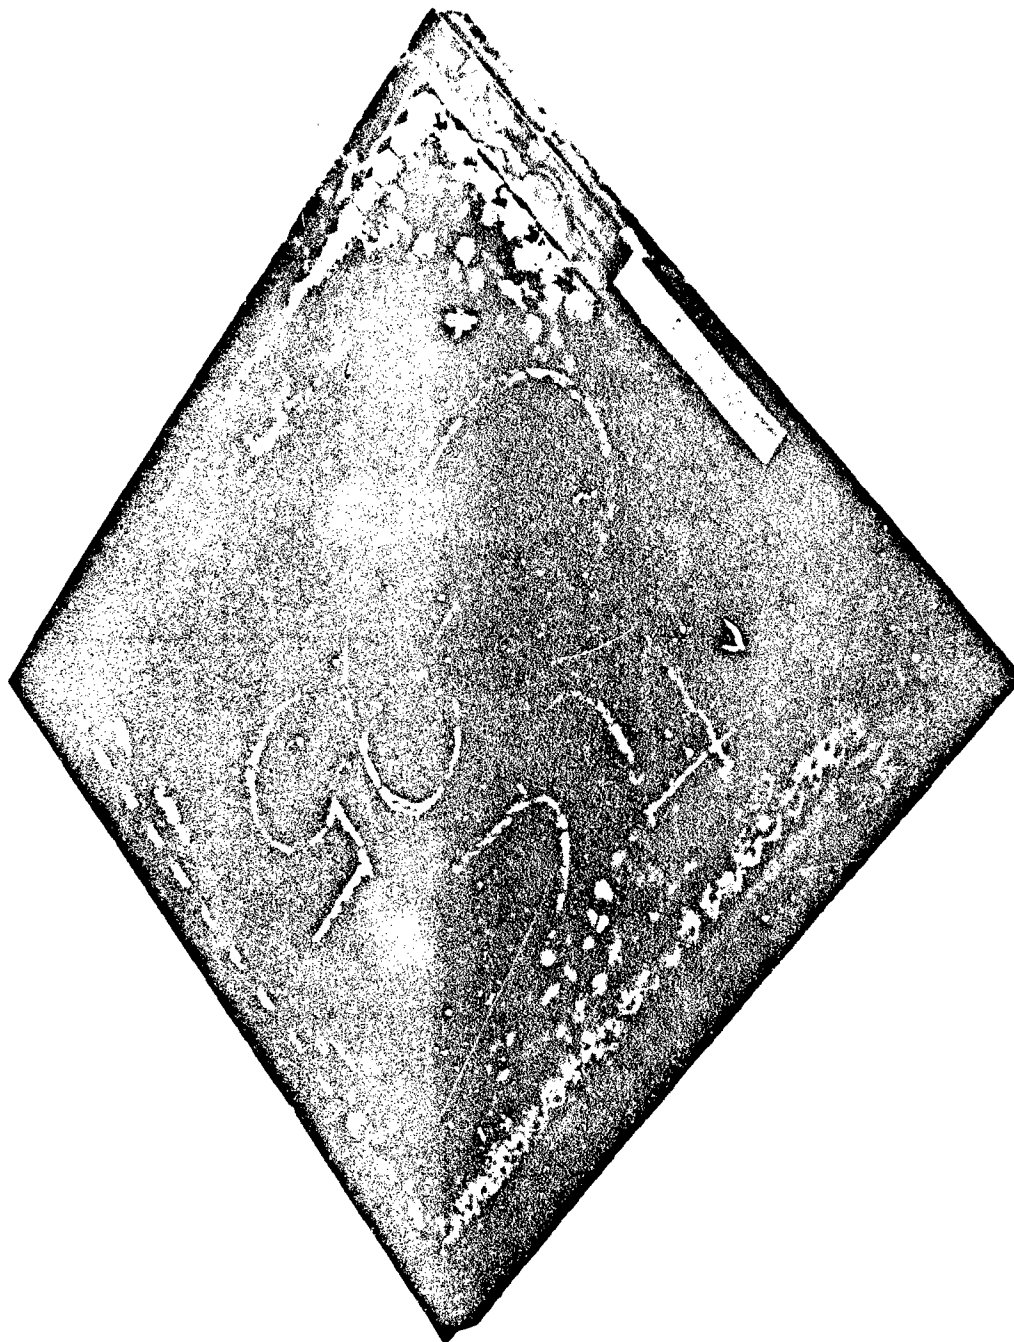


TITANIUM CARBIDE COMPOSITE ARMOR PLATE PRIOR TO BALLISTIC TESTING

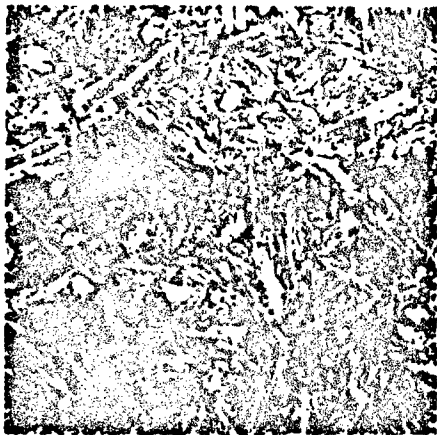

X1000

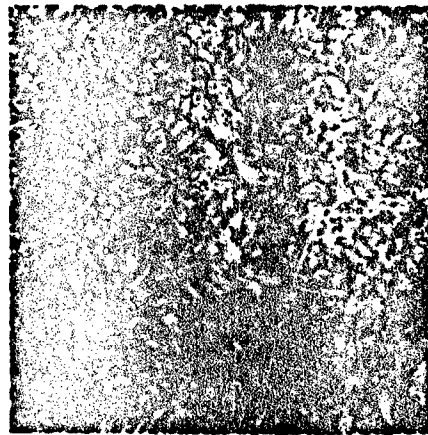

X1000

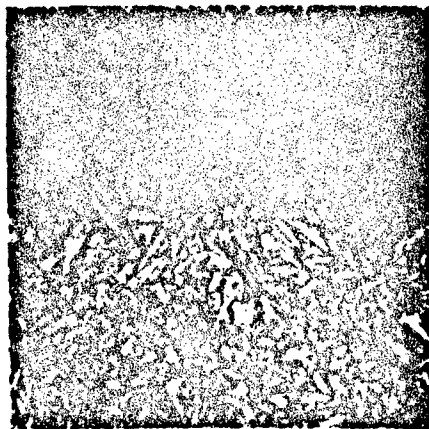


X1000

ETCHANT 4% PICRAL + 1 DROP HCl

PHOTOMICROGRAPHS OF STEEL ARMOR PLATE AFTER BRAZING




CALIBER 0.40 AP T32

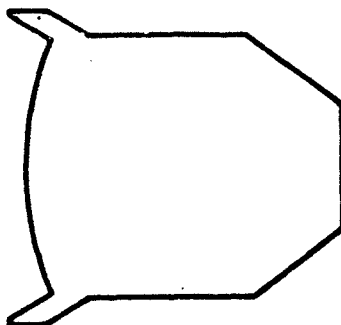

20MM FRAGMENT SIMULATING PROJECTILE




CALIBER 0.40 H188 WC CORE

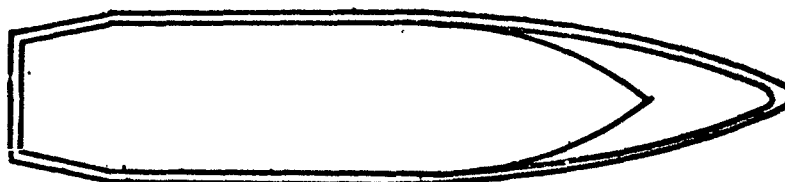

CALIBER 0.50 AP M2

**PROJECTILES USED TO DETERMINE BALLISTIC PERFORMANCE
OF WC AND TIC COMPOSITE ARMOR**


~~CONFIDENTIAL~~

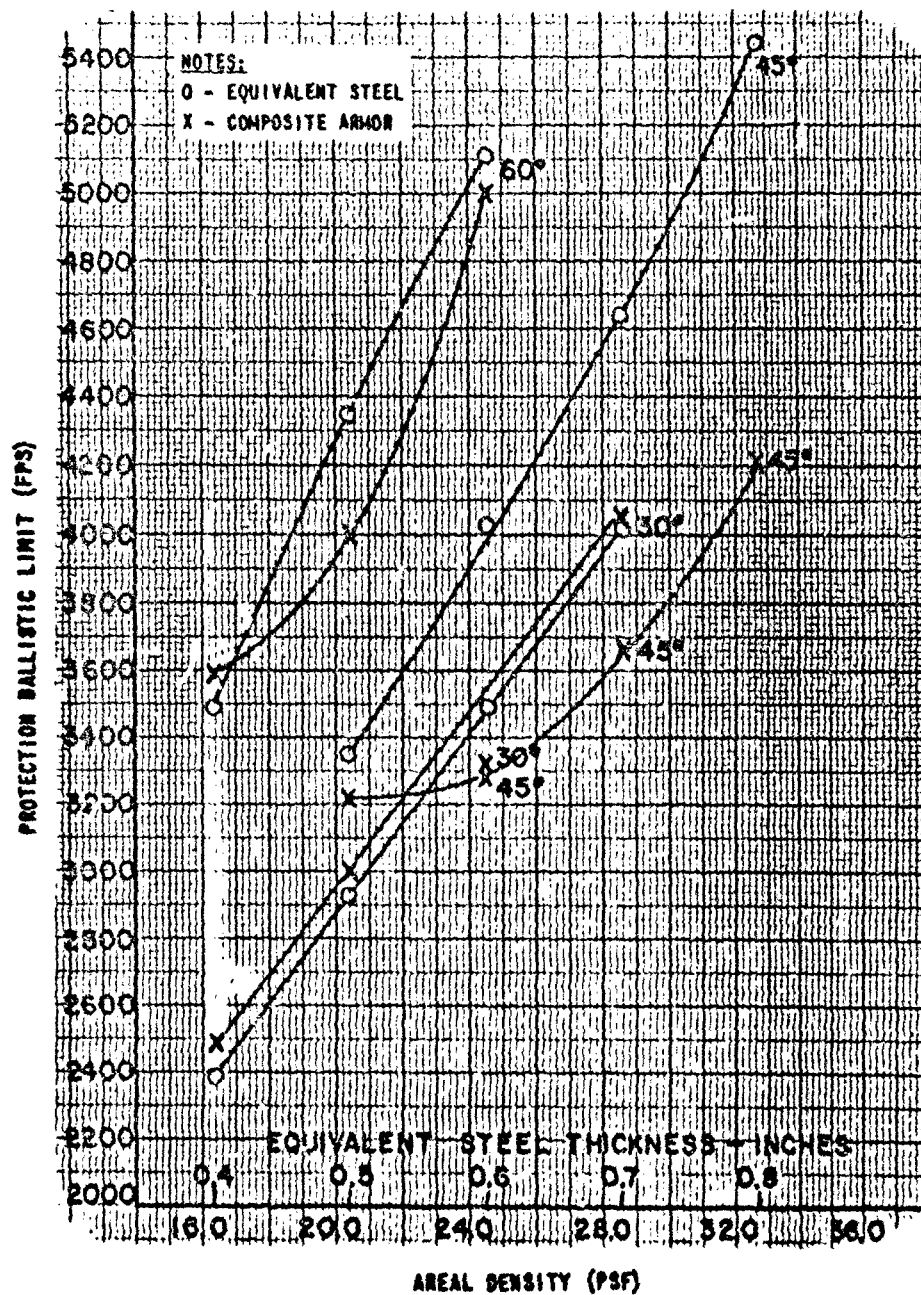

COMPARATIVE BALLISTIC PERFORMANCE OF WC COMPOSITE ARMOR WHEN ATTACKED
BY CALIBER 0.40 AP T33 SCALE MODEL PROJECTILES

~~CONFIDENTIAL~~


~~CONFIDENTIAL~~

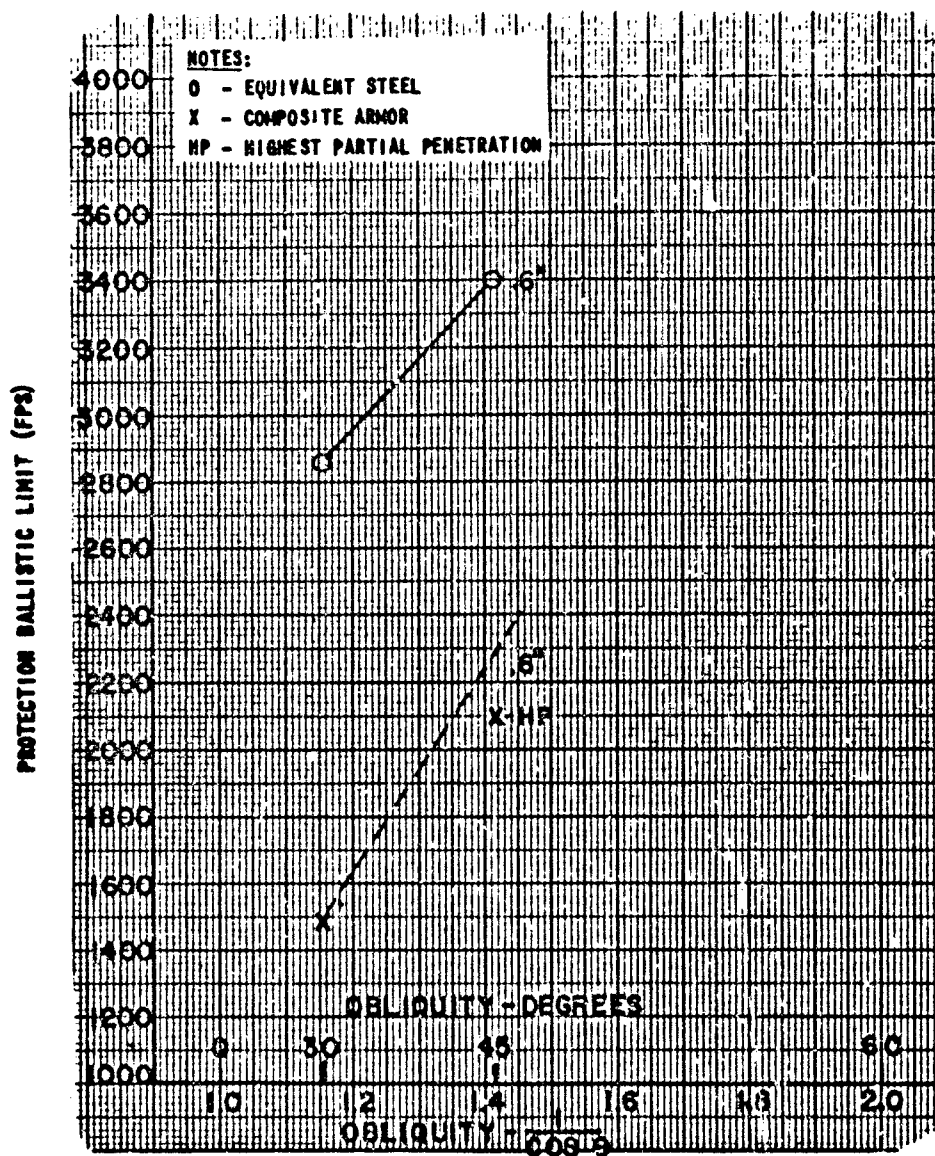

COMPARATIVE BALLISTIC PERFORMANCE OF WC COMPOSITE ARMOR WHEN ATTACKED
BY CALIBER 0.50 AP M2 PROJECTILES

~~CONFIDENTIAL~~


CONFIDENTIAL

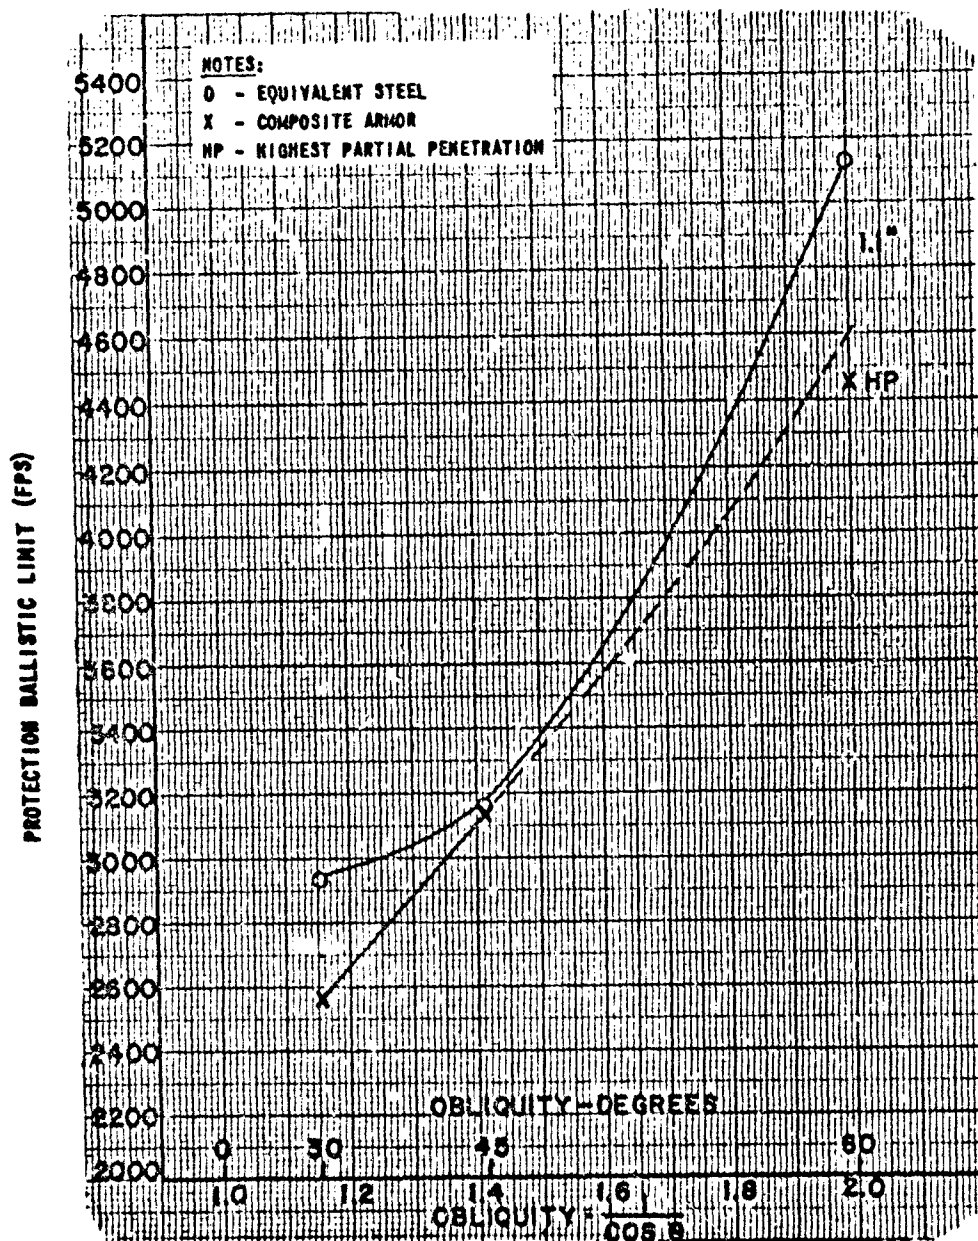

COMPARATIVE BALLISTIC PERFORMANCE OF WC COMPOSITE ARMOR WHEN ATTACKED
BY CALIBER 0.40 H198 WC CORES

CONFIDENTIAL


CONFIDENTIAL

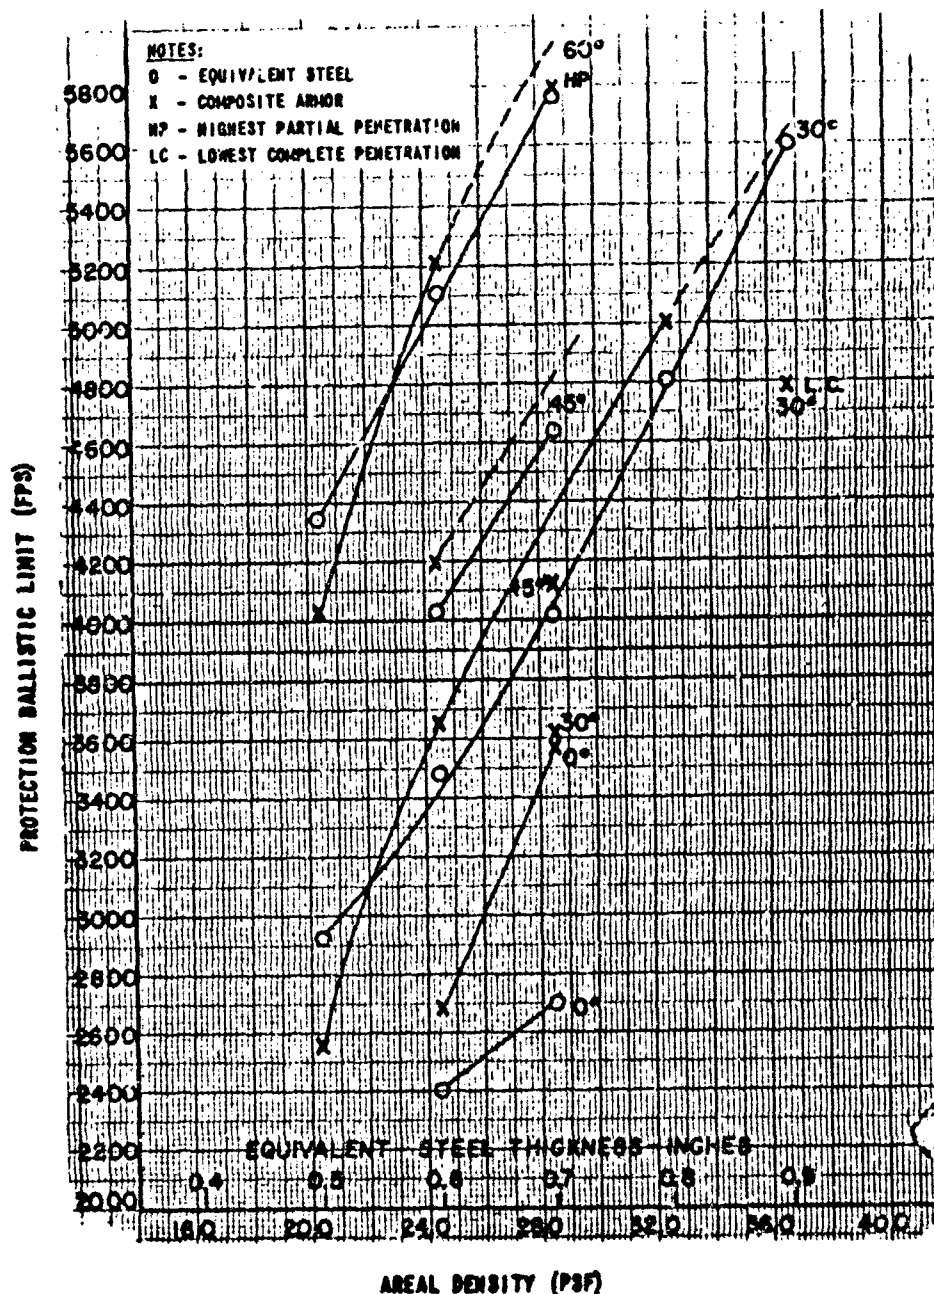

COMPARATIVE BALLISTIC PERFORMANCE OF TIC ARMOR WHEN ATTACKED
 BY CALIBER 0.40 AP T33 PROJECTILES

CONFIDENTIAL


~~CONFIDENTIAL~~

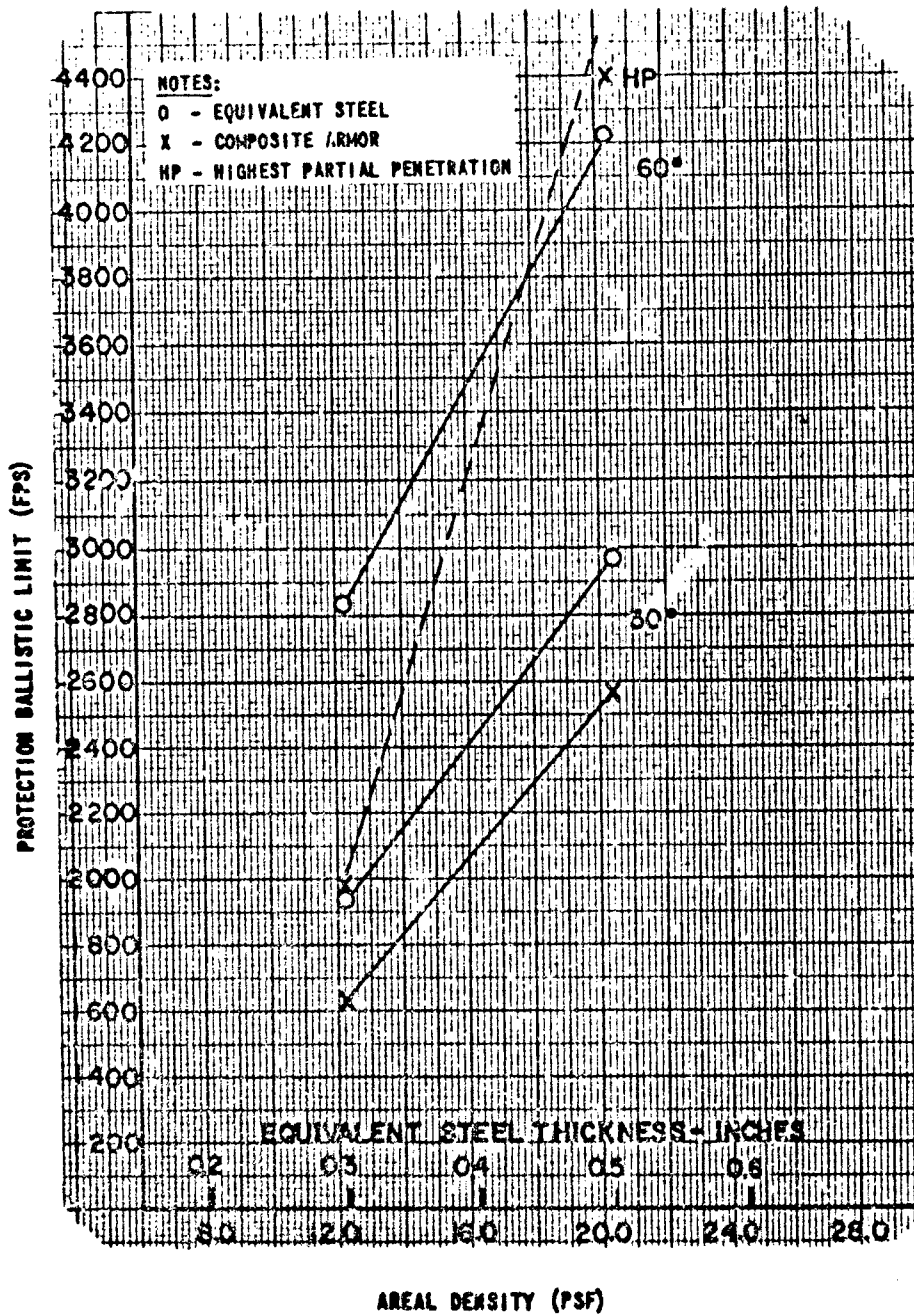

COMPARATIVE BALLISTIC PERFORMANCE OF TIC COMPOSITE ARMOR WHEN ATTACKED
20MM FRAGMENT SIMULATING PROJECTILES

~~CONFIDENTIAL~~

~~CONFIDENTIAL~~

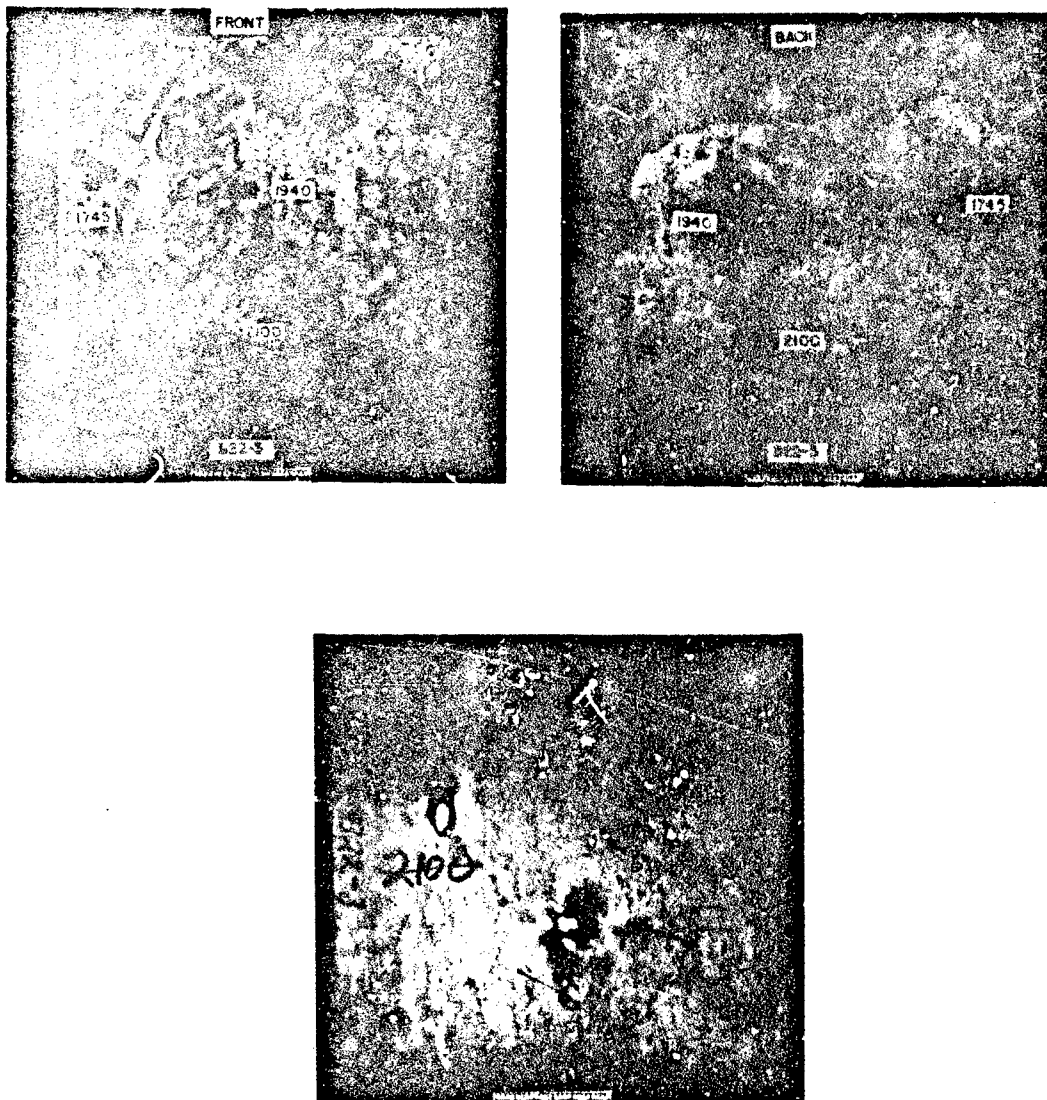

HADFIELD-MANGANESE SHEET


TUNGSTEN CARBIDE COMPOSITE ARMOR PLATE ATTACKED BY CALIBER 0.50
AP M2 PROJECTILES AT 45° OBLIQUITY

-23-

~~CONFIDENTIAL~~

FIGURE 11

CONFIDENTIAL

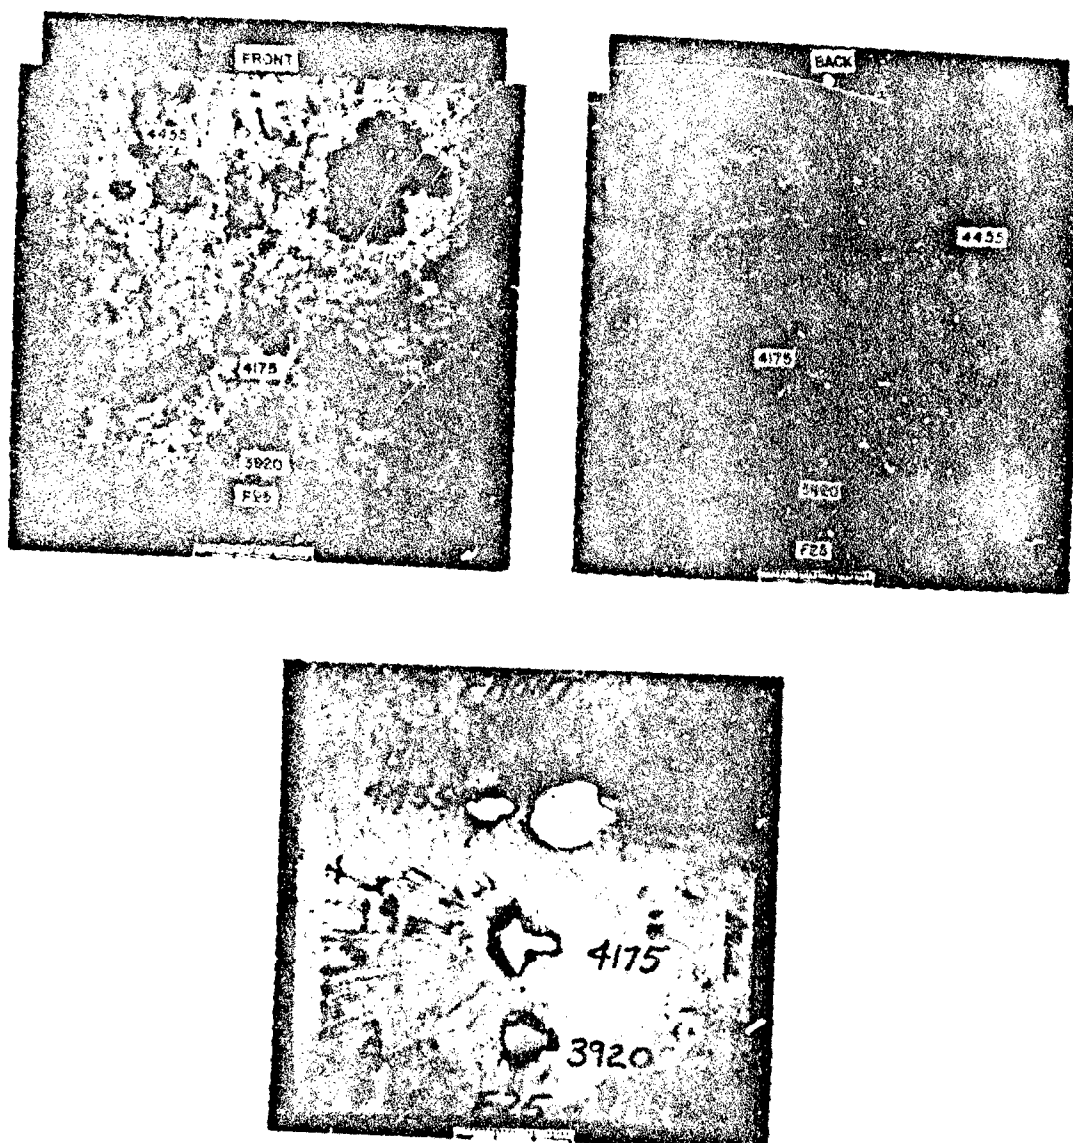




HADFIELD-MANGANESE SHEET
TUNGSTEN CARBIDE COMPOSITE ARMOR PLATE ATTACKED BY CALIBER 0.40
M19B WC CORES AT 60° OBLIQUITY

-24-

CONFIDENTIAL

FIGURE 12

~~CONFIDENTIAL~~

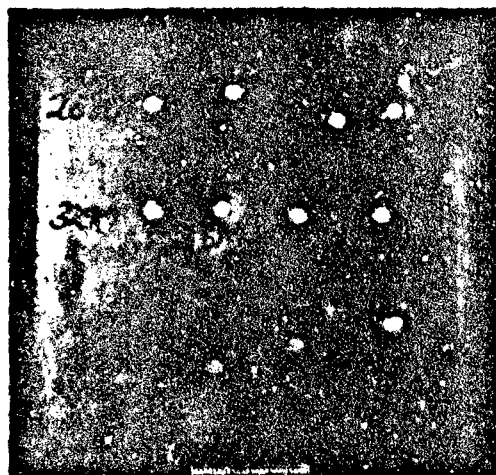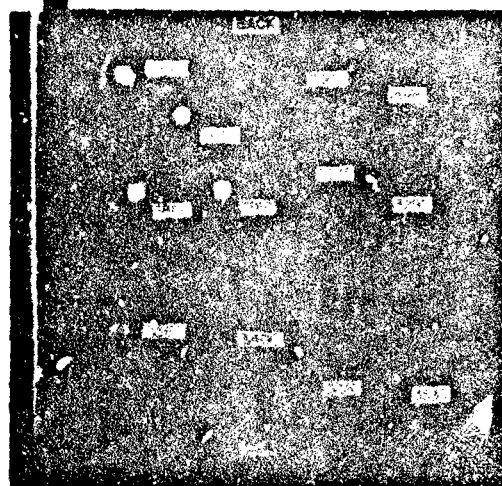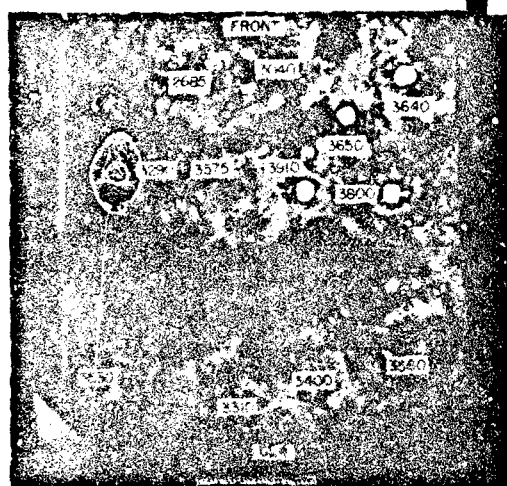


HADFELD-MANGANESE SHEET

TITANIUM CARBIDE COMPOSITE ARMOR PLATE ATTACKED BY CALIBER 0.40 AP T33
PROJECTILES AT 0° OBLIQUITY

~~CONFIDENTIAL~~

~~CONFIDENTIAL~~


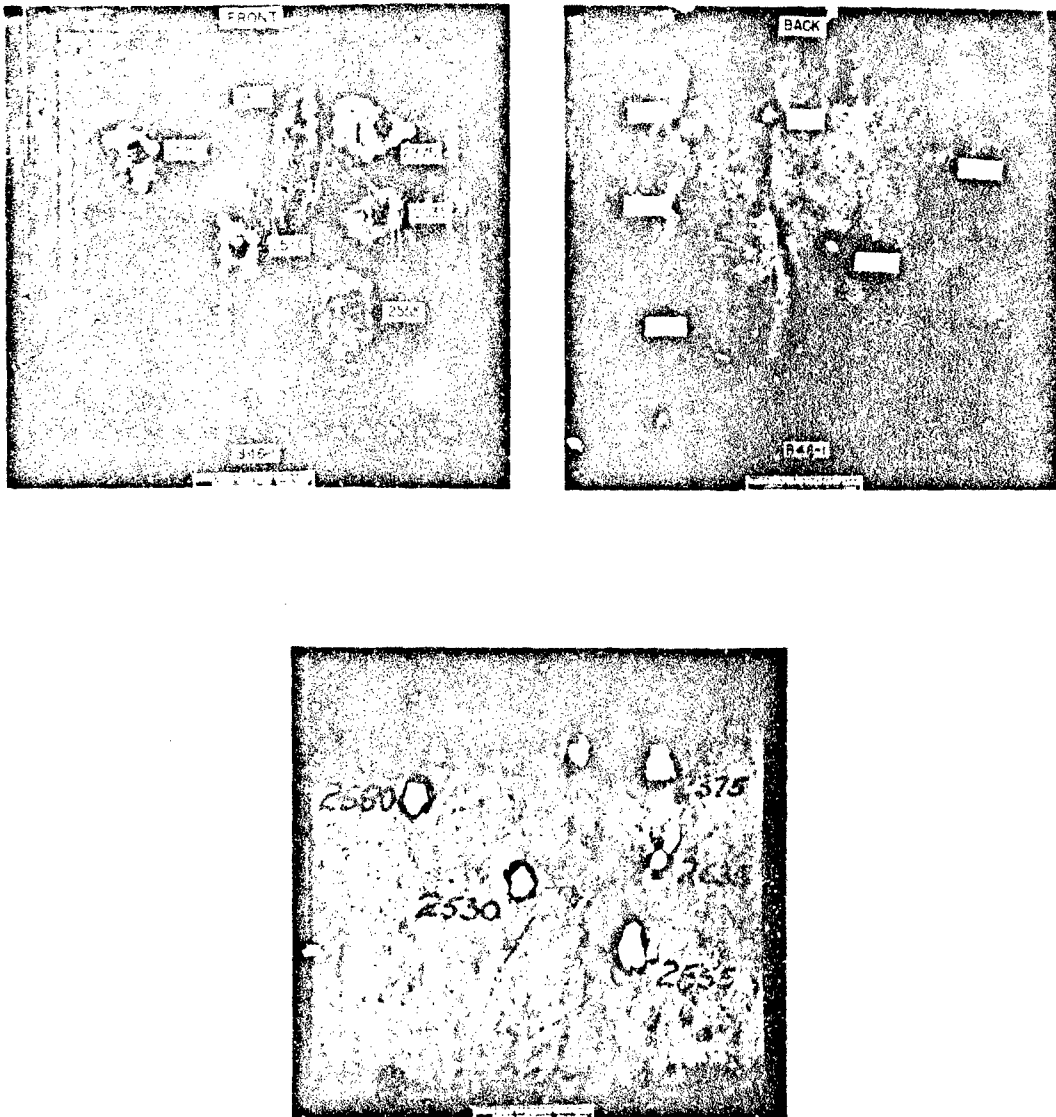


HADFELD-MANGANESE SHEET

TITANIUM CARBIDE COMPOSITE ARMOR PLATE ATTACKED BY CALIBER 0.40
AP T33 PROJECTILES AT 30° OBLIQUITY

~~CONFIDENTIAL~~



~~CONFIDENTIAL~~

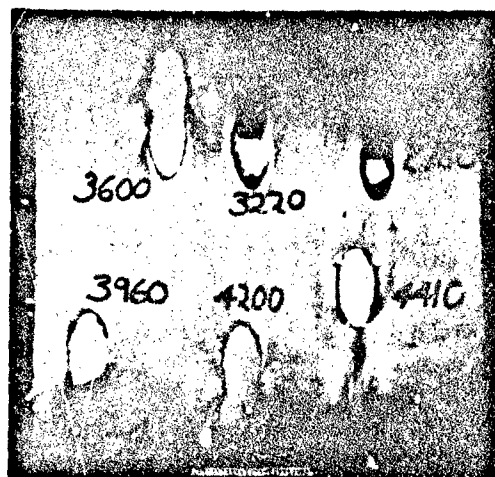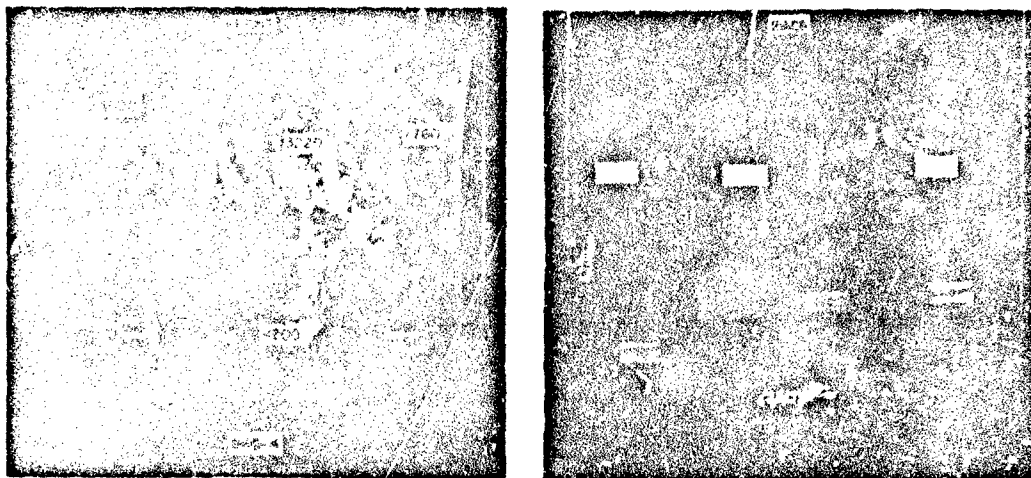

HADFIELD-MANGANESE SHEET

TITANIUM CARBIDE COMPOSITE ARMOR PLATE ATTACKED BY 20MM FRAGMENT
SIMULATING PROJECTILES AT 60° OBLIQUITY

~~CONFIDENTIAL~~

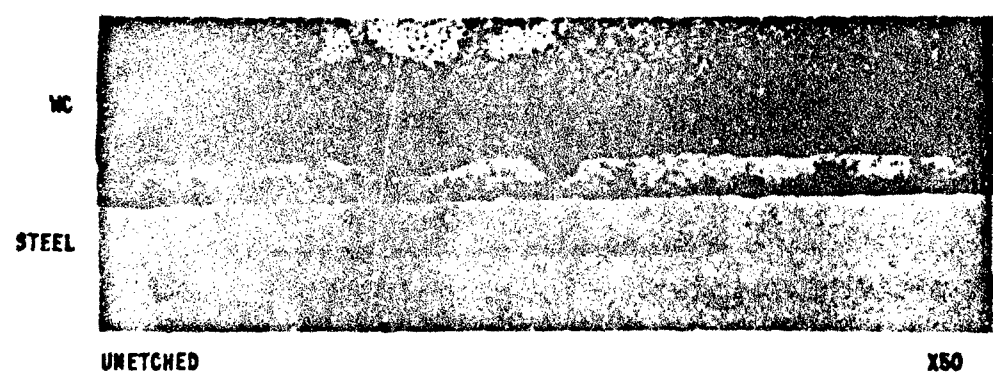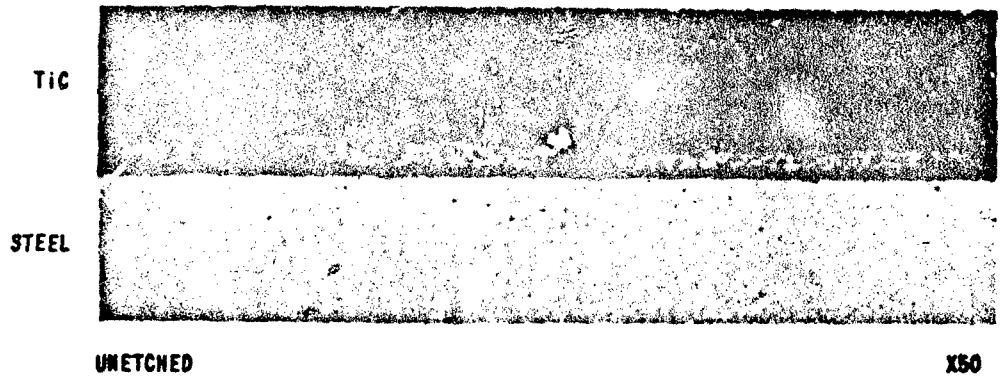

PHOTOMICROGRAPHS OF BRAZED JOINTS

~~CONFIDENTIAL~~

APPENDIX A

ROUND BY ROUND BALLISTIC DATA FOR WC AND TIC COMPOSITE ARMOR

TUNGSTEN CARBIDE

Projectile	Equivalent Steel Thickness (inch)	Obliquity (degrees)	Velocity (fps)	Scabbing Dimension (inches)	
				Length	Width
Caliber .40 AP T33	0.400	30	2510 CP	1 1/2	2
			2510 CP	2	1 1/2
			2000 FP	2 1/2	2
			2400 FP	2 1/2	2
			B. L. - 2425		
"	0.500	30	2045 CP	-	-
			2055 CP	-	-
			2030 FP	-	-
			2025 FP	-	-
			B. L. - 2092		
"	0.600	30	2380 CP	2	2
			2345 CP	4	4 1/2
			2335 FP	-	-
			2270 FP	2 1/2	4
			B. L. - 2320		
"	0.700	30	4120 CP	5	4
			4140 CP	2 1/2	4
			4005 FP	5	4
			3955 FP	-	-
			B. L. - 4000		
"	0.500	45	3120 CP	-	-
			3315 FP	-	-
"	0.600	45	B. L. - 3217		
			3220 CP	-	-
			3215 CP	-	-
			3210 FP	-	-
			3240 FP	-	-
"	0.700	45	B. L. - 3290		
			3270 CP	1	1
			3280 CP	2	2
			2740 FP	-	-
			2600 FP	-	-
"	0.800	45	B. L. - 3873		
			4200 CP	-	-
			4180 FP	-	-
			B. L. - 4215		
			3535 CP	2 1/2	2
"	0.400	60	3055 CP	2	1 1/2
			3050 FP	2	2
			3040 FP	2 1/2	2
			B. L. - 3005		
			4000 CP	2	2
"	0.400	80	4005 FP	-	-
			B. L. - 4005		

~~CONFIDENTIAL~~

~~UNCLASSIFIED - CONFIDENTIAL~~

TUNGSTEN CARBIDE (Cont'd)

Projectile	Equivalent Steel Thickness (inch)	Obliquity (degrees)	Velocity (fps)	Seabbing Dimension (Inches)	
				Length	Width
Caliber .40 AP T33	0.600	60	5020 CP	6	6
			5070 CP	-	-
			4985 PP	-	-
			4940 PP	7	7
				R.L. - 5004	
Caliber .50 AP M2	0.600	30	1455 CP	4	2
			1520 PP	4	4
				R.L. - 1488	
"	0.600	45	2100 PP	-	-
Caliber .40 H19B WC Cores	1.100	30	2645 CP	7	6
			2495 PP	-	-
				R.L. - 2565	
"	1.100	45	3185 CP	3	3
			3110 PP	-	-
				R.L. - 3148	
"	1.100	60	4455 PP	-	-

TITANIUM CARBIDE

Caliber .40 AP T33	0.600	0	2735 CP	-	-
			2640 CP	2	2 1/2
			2735 PP	1 1/2	1 1/2
			2665 PP	3 1/2	3
				R.L. - 2684	
"	0.700	0	3630 CP	2	2
			3640 CP	2	2 1/2
			3675 PP	1	1
			3600 PP	-	-
				R.L. - 3676	
"	0.800	30	2630 CP	-	-
			2610 CP	1 1/2	2
			2590 PP	-	-
			2555 PP	1	1 1/2
				R.L. - 2608	
"	0.600	30	3735 CP	2	2
			3680 PP	2	2
				R.L. - 3658	
"	0.700	30	3630 CP	-	-
			3610 PP	-	-
				R.L. - 3620	
"	0.800	30	5045 CP	6	6
			4970 PP	5	5
				R.L. - 5008	
"	0.800	30	4780 LC	-	-

~~UNCLASSIFIED~~

~~CONFIDENTIAL~~

~~CONFIDENTIAL~~

UNCLASSIFIED

TITANIUM CARBIDE (Cont'd)

Projectile	Equivalent Steel Thickness (inch)	Obliquity (degrees)	Velocity (fps)	Scabbing Dimension (inches)	
				Length	Width
Caliber .40 AP T33	0.600	45	4215 CP	3	3
			4270 CP	-	-
			4190 FP	3	4
			4120 FP	4	6
			R.L. - 4190		
"	0.700	45	4165 CP	2	3
			4210 CP	2½	3
			4075 FP	2	1½
			4060 FP	2½	3
			R.L. - 4187		
"	0.500	60	4060 CP	-	-
			3995 FP	2½	3
"	0.600	60	5315 CP	4	5
			5115 FP	-	-
"	0.700	60	5790 HP	-	-
			R.L. - 5215		
20MM FFP	0.300	30	1650 CP	6	6½
			1630 FP	6½	3½
			R.L. - 1640		
"	0.600	30	2550 CP	4	3
			2580 FP	-	-
"	0.300	60	2040 CP	-	-
			1915 FP	-	-
"	0.400	60	4410 CP	-	-
			R.L. - 1978		

NOTES: 1. CP - Complete Penetration
2. FP - Partial Penetration
3. HP - Highest Partial Penetration
4. LO - Lowest Complete Penetration

UNCLASSIFIED

~~CONFIDENTIAL~~

AD Accession No.

Vietnam Arsenal Laboratories, Watertown 72, Mass.
BALLISTIC EVALUATION OF ROLLED HOMOGENEOUS STEEL
ARMOR WITH TUNGSTEN CARBIDE AND TITANIUM CARBIDE
FACING (U) - Dominic A. Piccione

Report No. VAL TR 161.2/1 (C), Dec 1960, 31 pp -
tables - illus - appendix - ONS Code 5010.11.8090051
Confidential Report

(U) Ballistic testing was conducted to determine the
comparative performance of WC-steel and TiC-steel
composite armor when attached by cal. .40 N19B VC
cores, cal. .50 AP M2 projectiles, 20MM fragment
simulating projectiles, and cal. .40 AP T38 scale
model projectiles, at various obliquities. The com-
posite armor was compared to rolled homogeneous steel
armor on an areal density basis.

LIMITED DISTRIBUTION

UNCLASSIFIED

1. Terminal
ballistics,
testing
2. Ballistic
limits -
Protection

1. Piccione,
Dominic A.

II. ONS Code
5010.11.8090051

AD Accession No.

Vietnam Arsenal Laboratories, Watertown 72, Mass.
BALLISTIC EVALUATION OF ROLLED HOMOGENEOUS STEEL
ARMOR WITH TUNGSTEN CARBIDE AND TITANIUM CARBIDE
FACING (U) - Dominic A. Piccione

Report No. VAL TR 161.2/1 (C), Dec 1960, 31 pp -
tables - illus - appendix - ONS Code 5010.11.8090051
Confidential Report

(U) Ballistic testing was conducted to determine the
comparative performance of WC-steel and TiC-steel
composite armor when attached by cal. .40 N19B VC
cores, cal. .50 AP M2 projectiles, 20MM fragment
simulating projectiles, and cal. .40 AP T38 scale
model projectiles, at various obliquities. The com-
posite armor was compared to rolled homogeneous steel
armor on an areal density basis.

LIMITED DISTRIBUTION

UNCLASSIFIED

1. Terminal
ballistics,
testing
2. Ballistic
limits -
Protection

1. Piccione,
Dominic A.

II. ONS Code
5010.11.8090051

AD Accession No.

Vietnam Arsenal Laboratories, Watertown 72, Mass.
BALLISTIC EVALUATION OF ROLLED HOMOGENEOUS STEEL
ARMOR WITH TUNGSTEN CARBIDE AND TITANIUM CARBIDE
FACING (U) - Dominic A. Piccione

Report No. VAL TR 161.2/1 (C), Dec 1960, 31 pp -
tables - illus - appendix - ONS Code 5010.11.8090051
Confidential Report

(U) Ballistic testing was conducted to determine the
comparative performance of WC-steel and TiC-steel
composite armor when attached by cal. .40 N19B VC
cores, cal. .50 AP M2 projectiles, 20MM fragment
simulating projectiles, and cal. .40 AP T38 scale
model projectiles, at various obliquities. The com-
posite armor was compared to rolled homogeneous steel
armor on an areal density basis.

LIMITED DISTRIBUTION

UNCLASSIFIED

1. Terminal
ballistics,
testing
2. Ballistic
limits -
Protection

1. Piccione,
Dominic A.

II. ONS Code
5010.11.8090051

AD Accession No.

Vietnam Arsenal Laboratories, Watertown 72, Mass.
BALLISTIC EVALUATION OF ROLLED HOMOGENEOUS STEEL
ARMOR WITH TUNGSTEN CARBIDE AND TITANIUM CARBIDE
FACING (U) - Dominic A. Piccione

Report No. VAL TR 161.2/1 (C), Dec 1960, 31 pp -
tables - illus - appendix - ONS Code 5010.11.8090051
Confidential Report

(U) Ballistic testing was conducted to determine the
comparative performance of WC-steel and TiC-steel
composite armor when attached by cal. .40 N19B VC
cores, cal. .50 AP M2 projectiles, 20MM fragment
simulating projectiles, and cal. .40 AP T38 scale
model projectiles, at various obliquities. The com-
posite armor was compared to rolled homogeneous steel
armor on an areal density basis.

LIMITED DISTRIBUTION

UNCLASSIFIED

1. Terminal
ballistics,
testing
2. Ballistic
limits -
Protection

1. Piccione,
Dominic A.

II. ONS Code
5010.11.8090051

WATERTOWN ARSENAL.
WATERTOWN 72, MASS.

TECHNICAL REPORT DISTRIBUTION

Report No.:
WAL TR 161.3/1 (C)
December 1960

Title: Ballistic Evaluation of Rolled Homo-
geneous Steel Armor with Tungsten
Carbide and Titanium Carbide Facing (U)

Distribution List approved by Ordnance Materials Research Office,
1 December 1960.

No. of Copies	TO
1	Director, Army Research Office, Department of the Army, Washington 25, D. C.
1	Chief of Ordnance, Department of the Army, Washington 25, D. C. ATTN: ORDTB, Materials
1	Commanding General, Aberdeen Proving Ground, Maryland ATTN: Ballistic Research Lab.
3	ORDEE-LM, Technical Library, Bldg. 313
1	Commanding General, Army Ballistic Missile Agency, Redstone Arsenal, Alabama ATTN: Dr. G. H. Reisig
2	Commanding General, Frankford Arsenal, Philadelphia 37, Pa. ATTN: Pitman-Dunn Labs.
1	Commanding General, Ordnance Tank-Automotive Command, Detroit Arsenal, Center Line, Michigan ATTN: ORDMC-RM.1, Mr. Charles Salter
1	Commanding General, Ordnance Weapons Command, Rock Island, Ill. ATTN: ORDOW-IX
2	ORDOW-TX
1	Commanding General, U.S. Army Ordnance Special Weapons Ammu- nition Command, Dover, New Jersey
1	Commanding General, U.S. Army Rocket & Guided Missile Agency, Redstone Arsenal, Alabama ATTN: ORDAB-DV
5	ORDXR-RQA, Mr. R. L. Wetherington
1	ORDXR-RMO, Lt. E. J. Wilson
1	Commanding Officer, Detroit Arsenal, Center Line, Michigan ATTN: ORDIX-BPM
1	ORDIX-AL

Trans date: 1/28/61

No. of Copies	TO
1	Commander, Naval Ordnance Test Station, China Lake, California ATTN: Code 5557
1	Director, Naval Research Laboratory, Anacostia Station, Washington, D. C. ATTN: Technical Information Officer
1	Commander, Naval Weapons Laboratory, Dahlgren, Virginia ATTN: A & P Lab.
10	Commander, Armed Services Technical Information Agency, Arlington Hall Station, Arlington 12, Virginia ATTN: TIPDR
1	U.S. Atomic Energy Commission, Office of Technical Informa- tion Extension, P. O. Box 62, Oak Ridge, Tennessee
1	Defense Metals Information Center, Battelle Memorial Institute, Columbus, Ohio, THRU: Commanding Officer, Ordnance Materials Research Office, Watertown Arsenal, Watertown 72, Mass., ATTN: RPD
1	National Aeronautics & Space Administration, 1520 H Street, N. W., Washington 25, D. C.
1	The Director, Jet Propulsion Laboratory, California Institute of Technology, Pasadena 3, California ATTN: Dr. L. Jaffe
1	Dr. W. R. Lucas, George C. Marshall Space Flight Center, Huntsville, Alabama ATTN: M-S&M-M
1	Mr. W. A. Wilson, George C. Marshall Space Flight Center, Huntsville, Alabama ATTN: M-F&AE-M, Bldg. 4720
2	Commanding General, Aberdeen Proving Ground, Maryland ATTN: ORDBG - Dev. & Proof Serv., Armor Br.
1	ORDBG - Technical Branch
1	Ordnance School
1	Commanding General, Continental Army Command, Fort Monroe, Va. ATTN: Res. & Dev. Section
1	Commanding Officer, Eng. Res. & Dev. Laboratories, Fort Belvoir, Virginia ATTN: Metallurgist Tech. Serv. Dept.

No. of
Copies

TO

1 Commanding Officer, Diamond Ordnance Fuze Laboratories,
Washington 25, D. C.
ATTN: ORDTL .012, Technical Reference Branch

1 Commanding Officer, Office of Ordnance Research, Box CM,
Duke Station, Durham, North Carolina
ATTN: ORDOR-ED

1 Dr. Peter Kosting

1 Commanding Officer, Ordnance Materials Research Office,
Watertown Arsenal, Watertown 72, Massachusetts
ATTN: RPD

1 Commanding Officer, Picatinny Arsenal, Dover, New Jersey
ATTN: Feltman Research Labs

1 Commanding Officer, Rock Island Arsenal, Rock Island, Illinois
ATTN: Laboratory

1 Commanding Officer, Springfield Armory, Springfield 1, Mass.
ATTN: ORDED-TX

1 Commanding Officer, Watervliet Arsenal, Watervliet, New York
ATTN: ORDEF-RT

1 Army Reactor Branch, Division of Research Development,
Atomic Energy Commission, Washington 25, D. C.

1 Commander, Wright Air Development Division, Wright-Patterson
Air Force Base, Ohio
ATTN: WWRCEE

1 Chief, Bureau of Ships, Department of the Navy,
Washington 25, D. C.
ATTN: Code 341

1 Chief, Bureau of Naval Weapons, Department of the Navy,
Room 2225, Munitions Bldg., Washington 25, D. C.
ATTN: RMWP

1 Chief, Office of Naval Research, Department of the Navy,
Washington 25, D. C.
ATTN: Code 423

1 Chief, Naval Engineering Experimental Station, Department of
the Navy, Annapolis, Maryland

UNCLASSIFIED

No. of Copies	TO
1	President, Continental Army Command, Board No. 2, Fort Knox, Kentucky
1	President, Continental Army Command, Board No. 3, Fort Benning, Georgia
1	Office, Ordnance Tech. Rep., United States Army, Ottawa, Ontario, Canada ATTN: U.S. Tech. Rep.
5	Commanding Officer, Watertown Arsenal, Watertown 72, Mass.
1	ATTN: ORDBE-LIM, Technical Information Section Author
71	-- TOTAL COPIES DISTRIBUTED

71 - Total number of copies printed.

Cy#5- retention - Advanced Research
Projects Agency
Pentagon, 30155-
Washington 25, D.C.
Attn: Commander E. C. Pears, USN

UNCLASSIFIED